

Armed Services Technical Information Agency

Because of our limited supply, you are requested to return this copy WHEN IT HAS SERVED YOUR PURPOSE so that it may be made available to other requesters. Your cooperation will be appreciated.

AD

28618

NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY OTHER PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.

Reproduced by
DOCUMENT SERVICE CENTER
KNOTT BUILDING, DAYTON, 2, OHIO

UNCLASSIFIED

AD NO. 28618

ASTIA FILE COPY

ELEVENTH QUARTERLY PROGRESS REPORT

FERRITE DEVELOPMENT
CONTRACT NO.: DA-36-039-sc-5449
GENERAL CERAMICS & STEATITE CORP.
Kearney, N.J.

11th QUARTERLY PROGRESS REPORT
SIGNAL CORPS CONTRACT NO. DA36-039 sc-5449
Period: 1 Oct. - 31 Dec., 1953

MAGNETIC FERRITES

GENERAL CERAMICS AND STEATITE CORPORATION

Kearney, New Jersey

No. of Copies Received: 50

No. of
Copies

DISTRIBUTION OF REPORTS

- 1 - Chief, Engineering & Technical Division, Office of Chief Signal Officer, Dept of the Army, Washington 25, D. C., ATTN: SIGGD-P1
- 2 - Commander, WADC, Wright-Patterson Air Force Base, Ohio, ATTN: WCLCO-2
- 1 - The Director, U.S. Naval Research Laboratory, Code 2021, Washington 25, D.C.
- 1 - Chief, Bureau of Ships, Dept of Navy, Washington 25, D.C., ATTN: Code 817D
- 1 - Commanding Officer, U.S. Navy Underwater Sound Laboratory, New London, Conn.
- 1 - Office of Inspector of Naval Material, Navy Building, 495 Summer Street, Boston 10, Mass., For Trans-Sonic Lot II, Contract No(s) 9763
- 1 - Chief, Bureau of Ordnance, Navy Department, Washington 25, D. C.
- 1 - Commander, Naval Ordnance Laboratory, White Oak, Silver Spring 19, Maryland
- 1 - Chief, Bureau of Aeronautics, Dept of the Navy, Washington 25, D. C.
- 1 - Commander, Rome Air Development Center, Electronic Development Div., (RCR) Griffiss Air Force Base, Rome, N. Y.
- 1 - Commander, Air Force Cambridge Research Center, CRRAL, 230 Albany St., Cambridge 39, Mass.
- 1 - Director, Nat'l Bureau of Standards, Washington 25, D.C., ATTN: Division 14.0
- 1 - U.S. Dept of Commerce, Nat'l Bureau of Standards, Corona, California
- 1 - Technical Reports Library, ESL
- 1 - Contract File
- 1 - Director of Engineering, Hqs., SCEL
- 1 - Bu. of Mines, U.S. Dept of the Interior Electrotechnical Lab., Norris, Tenn.
- 1 - Research & Development Board, Pentagon Building, Washington 25, D. C.
- 5 - Armed Services Technical Information Agency, Document Service Center, Knott Building, Dayton 2, Ohio
- 1 - Federal Telecommunications Labs., Inc., 500 Washington Ave., Nutley 10, N.J., ATTN: Mr. F. A. Muller, Dept R-17
- 1 - Philips Laboratories, Inc., Irvington-on Hudson, New York
- 1 - Massachusetts Institute of Technology, Laboratory for Insulation Research, Cambridge 39, Mass., ATTN: Librarian
- 1 - Chief of Ordnance, Washington 25, D.C., ATTN: ORDTB-Materials
- 1 - Chief of Ordnance, Washington 25, D.C., ATTN: ORDTX-AR
- 2 - Commanding General, Redstone Arsenal, Huntsville, Ala., ATTN: Tech Library
- 1 - Commanding Officer, Frankford Arsenal, Philadelphia 37, Pa., ATTN: ORDBA-FEL
- 1 - Commanding Officer, Watertown Arsenal, Watertown, Mass., ATTN: OMRO
- 1 - Project Whirlwind, Digital Computer Laboratory, Dept of Elec. Engr., MIT 211 Massachusetts Ave., Cambridge 39, Mass., ATTN: Project Librarian
- 1 - Chief, Technical Intelligence Branch, ERDL, Corps of Engineers, Fort Belvoir, Va.
- 1 - Task Order No. EDG6, Engineering Research Institute, University of Michigan, Ann Arbor, Michigan, ATTN: Mr. D.M. Grimes
- 1 - CGS Laboratories, 391 Ludlow St., Stamford, Conn., ATTN: Mr. C.S. Sondheimer, Pres
- 1 - Laboratory for Magnetic Research, Dept of Physics, Carnegie Institute of Technology, Pittsburgh, Pa., ATTN: Prof. J. E. Goldman
- 1 - Dept of Physics, University of California, Berkeley 4, California, ATTN: Prof. Charles Kittel

11th QUARTERLY PROGRESS REPORT
GENERAL CERAMICS AND STEATITE CORPORATION
SIGNAL CORPS CONTRACT NO. DA36-039 sc-5449

No. of Copies Received: 50

No. of
Copies

DISTRIBUTION OF REPORTS

- 1 - Magnetic Materials Dev. Laboratory, Materials Engineering Dept., Westinghouse Electric Corp., 501 Highland Ave., East Pittsburgh, Pa., ATTN: J.A. Osborn
- 1 - Countermeasures Branch, ESL, Search & Intercept Section, ATTN: Mr. L. Mond
- 1 - Component Parts Section, C&MB, SSL, ATTN: S. Danko
- 1 - British Liaison Office, ASES, THRU: Security & Intelligence, Hqs., SCEL
- 1 - Canadian Army Staff, THRU: Security & Intelligence, Hqs., SCEL
- 1 - Canadian Dept of Defense Production, THRU: Security & Intelligence, Hqs., SCEL
- 1 - Mail and Records, SSL
- 4 - Reserve

This contract is supervised by the Components & Materials Branch, SSL, SCEL. For further technical information, contact SSL, Fort Monmouth, N.J., Eatontown 3-1060, Extension 2662, Project Advisor, Dr. E. Both, Engineer, Materials Section.

ELEVENTH QUARTERLY PROGRESS REPORT

CONTRACT FOR SERVICES, FACILITIES, AND MATERIALS
REQUIRED TO INVESTIGATE AND STUDY MAGNETIC FERRITES

PERIOD COVERED: From October 1, 1953 to December 31, 1953

CONTRACT NO. DA 36-039-sc-5449

DEPT. OF ARMY PROJECT NO.: 3-93-00-503, 3-99-04-042

SIGNAL CORPS PROJECT NO.: 32-2005-D, 29-194B

PLACED BY: Laboratory Office, Signal Corps Procurement Agency
Contracting Division, Fort Monmouth, New Jersey

CONTRACTORS: General Ceramics and Steatite Corporation
Keasbey, New Jersey

OBJECT: To develop ferromagnetic ferrites of different permeabilities, and low magnetic losses, and to investigate conditions favorable to their production.

REPORTED BY: Dr. E. Albers-Schoenberg, Supervisor
Ephraim Gelbard, Project Engineer

Title Page	Page 1
Table of Contents	Page 2
List of Graphs and Tables	Page 3
Abstracts	Page 4
PART I Body Development and Measurements Made During the Eleventh Quarter of the Con- tract 1953/1954 DA Project No. 3-93-00-503 SC Project No. 32-2005-D	
A) Temperature Stable Bodies of the Lower Permeability Range (Improvement of the Reproducibility of MF 90, "B" body	Page 5
B) New Measurements of Ferramic Q	Page 7
C) Comparison of Measurement Techniques for Initial Permeability and Q	Page 8
PART II Body Development and Measurements During the Third Quarter of the Contract 1953/1954 DA Project No. 3-93-00-503 SC Project No. 32-2005-D	
A) Investigation of Reproducibility and Uni- formity of Ferrite Materials (Continuation)	Page 9
PART III Research Planned for Next Quarter	Page 13
PART IV Manhours Spent on Contract for the Period of 10-1-53 to 12-31-53	Page 14

LIST OF GRAPHS & TABLES

<u>GRAPH NO.</u>	<u>DESCRIPTION</u>
172	Initial Permeability vs. Temperature for MF-1835 A, B & D
173	Initial Permeability vs. Temperature for MF-1835-B at Three Firing Temperatures
174	Distribution of μ_0 (1 Mc) for MF-141-"I" body, Two Preparations; Two Particle
175	Sizes, Two Die-Pressures

TABLE NO.

LII	Properties of New "B"-Body Type Compositions
LIII	Comparison of Magnetic Properties of Ferramic "Q" (Preliminary Data) with Two Other Low-Poss Ferrites
LIV	Comparison of μ_0 and Q by Various Measurement Methods (1 Mcs) (F-268 Toroid)
LV	Distribution of μ_0 (1 Mcs) MF-141-"I" at 27°C for Two Calcines Two Different Particle Sizes, and Two Different Pressures Die F-109 - (Percentages of Cores Within $\pm 2\frac{1}{2}\%$ and $\pm 5\%$ for μ_0 Using the Peak of the Distribution Curves as the Center Value)

ABSTRACTS

PART I

- A) The investigation of temperature-stable bodies of the lower permeability range has been continued. The work reported upon refers to the "fluxed" type similar to the old General Ceramics formula MF-90-"B". The effect of various fluxes and various firing temperatures has been studied. From the viewpoint of future production, the results are promising.
- B) A preliminary property chart of Ferramic Q, a new low-loss, low-permeability body, is presented.
- C) Three different methods of measuring μ_0 and Q are compared. For a number of materials, the deviation of results is too large. Especially for the low-loss body, Ferramic Q, the figures are erratic.

PART II

- A) The Reproducibility and Uniformity investigation has been extended on material MF-141-"I". Results for μ_0 measurements on 400 cores (in the virgin state) are reported. One out of 6 batches shows 98% of all cores to fall within a tolerance of $\pm 2\frac{1}{2}\%$. Some conditions for high uniformity are established.

PART I

Body Development and Measurements Made During The
Eleventh Quarter of the Contract
DA Project No.: 3-93-00-503, S. C. Project No.: 32-2005-D

A) Temperature Stable Bodies of the Lower Permeability
Range (Improvement of the Reproducibility of MF 90-
"B" Body)

The majority of the program in temperature stability this quarter has been directed to the development of body MF 1835, a variation of the standard body, MF-90-"B". The body MF 1835 is an attempt to duplicate the "B"-body with the exception that puror raw ingredients are used.

The original body MF-90 as it was formulated in 1948 contained raw materials from natural sources. The natural impurities of these materials contributed to the peculiar temperature behaviour of the body, however, inconsistencies of composition were inevitable and reproducibility of μ_0 , Q, and temperature coefficient of μ_0 were frequently not attainable.

The aim of this part of our work was to duplicate the Ferramic "B" material by using pure raw materials only; i.e., to add the former impurities in the form of pure reagents. "Pure" in this case means the grade of purity, mostly better than 99%, as it is represented in technical raw materials.

Since silica and Ca-compounds are the most usual impurities in natural ores, a hydrated silica and calcium fluoride or calcium carbonate were added. After various attempts with additions of either silica or calcium compounds or both, and after discarding all those which failed to give a body approaching the B-body properties, finally the composition was established with an addition of 2.0% to 3.0% of silica (computed as water-free SiO_2) and CaF_2 in a fixed amount of 2.75% or calcium carbonate of 3.50%. The other (main) ingredients of the body remained essentially the same as those of the B-body:

5% MgO
6% MnO_2
10% ZnO
6% NiO

The remainder Fe_2O_3 , which amounted to 68% in the case of high silica content and to 69% in the case of low silica content.

PART I (Cont'd.)

A) Cont'd.

The results of % $\Delta\mu_o$ vs Temperature are shown in Graphs 172 and 173. μ_o These represent the best obtainable up to the present. For further details see Table LII.

Out of the four compositions (MF-1835A to MF-1835D) the A and D variations appear the most promising (see Graph 172). MF-1835A shows a low negative temperature coefficient of about $-.014\%/^{\circ}\text{C}$ from 30°C to 100°C . The initial permeability of this body is 90 and the Q is 90 (toroidal measurements at 1 Mcs). MF-1835D has a positive temperature coefficient of about $+.028\%/^{\circ}\text{C}$ from 30°C to 100°C . The initial permeability is 88 and the Q is 81 (toroidal measurements at 1 Mcs).

Graph 173 shows the effect of firing temperature on MF-1835B. It is clearly demonstrated here that the sign and magnitude of the temperature coefficient can be greatly changed by firing variations.

It has to be mentioned that MF-1835D is made without pre-calcining the materials. Therefore, it shows a relatively high shrinkage which is undesirable for a production body. It is, however, presumed, that body MF-1835D could be modified accordingly as to yield similar qualities after the raw mixture has undergone a prefiring treatment.

In any case, for all of these bodies, there remains a remarkable sensitivity as to the temperature coefficient of μ_o . A small coefficient easily changes its sign. At high temperatures from about 220°C on all curves as shown on Graph 172, turn positive and the coefficient increases rapidly toward the Curie point.

Summarizing, it may be stated that the goal has been reached and the temperature stable "B" composition, which has found widespread application during the past three or four years, has successfully been reshaped. The knowledge of proper handling a temperature stable body of the "fluxed" type has been greatly amplified.

Further development of the body MF-1832C (mentioned in the last quarterly report) has been aimed at determining the degree of firing required by that body in its present state of formulation. Numerous firings have disclosed that various shapes of the ferrite ware will affect the maturing temperature. F-108 (about 2" O.D., 1.5" I.D., 1/4" thick) mature at a slightly lower temperature than the F-256 tuning slugs (about 1/2" O.D., 1/4" I.D., 1-1/2" long). Good results have been obtained in both cases.

A few attempts to increase the effective fired density of MF-1829 have proved unsuccessful. In view of the better performance of the body MF-1832C, work on MF-1829 has been abandoned and MF-1832C can be adopted as a temperature stable ferrite of the permeability class 170-180 if necessary.

B) New Measurements of Ferramic Q

As indicated in the last quarterly progress report, more details of this ferrite are now shown. Table LIII gives preliminary measurements of this material in comparison with two other low-loss ferrites.

Ferramic "Q" is the lowest loss ferrite that has yet been developed. Some preliminary data shows it to have a useful frequency range at least up to 30 Mcs. The losses at 1 Mcs are so low that considerable difficulty has been experienced in evaluating the true $\tan \delta$ (see Section C).

In all aspects (regarding losses, temperature stability, inherent magnetic stability), this material is considered to be a most significant development.

C) Comparison of Measurement Techniques for Initial Permeability and Q

Since the last Quarterly Progress Report in which the field strength of the 1 Mcs μ_0 measurement (R. F. Bridge) was evaluated, the attempt has been made to compare various measurement techniques with the objective of improving both accuracy and speed. On a set of F-268 toroids (O.D. = 1.25", I.D. = 0.75"), three different methods have been used and a fourth is being worked on. The three measurement methods already performed were:

- 1) R. F. Bridge (G. R. 916A)
- 2) Q-meter (Boonton 260-A)
- 3) R. F. Permeameter* (National Electronic Laboratories, Size B)

The first two methods utilized a toroidal winding (N=25 No. 20 AWG SF, evenly distributed), the third method needs no winding. All the measurements were performed at 1 Mcs to lend correlation to all previous work done on the R. B. Bridge at 1 Mcs.

Table LIV summarizes these results. The fourth method will consist of the evaluation of permeability by the measurement of H and B on a toroidal winding. When this is completed, an attempt to analyze the differences between the various methods will be made.

As indicated in Section B, an attempt was made to measure the losses of Ferramic Q by these three methods. All the results are fairly doubtful and cannot be trusted as a true indication of the material for the following reasons:

On the R. F. Bridge, the loss resistance is so small that accurate reading is extremely difficult ($R = 0.2$ ohms). If the copper losses are then subtracted, the loss resistance approaches zero (or infinite Q). On the R. F. permeameter, this ferrite yields a negative $\tan \delta$ m. On the Q-meter, a readable value can be measured but if the Q is over 500-600 the Q-meter accuracy is greatly reduced. It appears that other methods must be found to evaluate this material if further development is to be made.

*Developed by P. H. Haas, National Bureau of Standards

PART II

Body Development and Measurements Made During the Fourth Quarter of the Contract

DA Project No.: 3-99-04-402, S. C. Project No.: 29-194-B

A) Investigation of Reproducibility and Uniformity of Ferrite Materials

Since the initial phase of the work had been completed on Ferramic "G"-MF-254 in the last quarterly report, the uniformity and reproducibility investigation started over again with Ferramic "I"-MF-141. This ferrite material has been subjected to a very similar procedure of preparation, sample-pressing, firing and measurement. The μ_0 figures have been taken from the cores in the virgin state and are reported and evaluated in the same manner as exercised for MF-254-"G" material. Another set of measurements, after magnetization and demagnetization, will follow; as well as the more important measurements of reversible permeability.

Preparation of the samples comprised the following steps of procedure:

A mix consisting of the following:

- 665 grams nickel oxide, grey
- 1645 grams zinc oxide, French process
- 1540 grams iron oxide, red, tech. grade,
(C. K. Williams)
- 6700 ccm tap water

was milled for four hours with 7 kg of steel balls (3/8" diameter). Then, an additional 3150 grams of iron oxide (red), and 4800 ccm water were added and the milling continued for another four hours. After emptying and drying, the dry cakes were granulated through an 8-mesh screen, and the granulation filled into saggars for calcining.

At this point the preparation has been divided into two parts; each part being subjected to a separate calcining heat treatment. Sixty percent of the material was fired two hours at 1900°F, forty percent for the same time at 2250°F.

From these two calcines, two bodies have been prepared according to the following formulae:

PART II (Cont'd.)

MF-141-L (L standing for low-fired calcine)

80% by weight low-fired calcine
1.9% by weight of nickel oxide grey
4.7% by weight of zinc oxide, French process
13.4% by weight of iron oxide (red), techn. grade

MF-141-H (H standing for high-fired calcine)

50% by weight high-fired calcine
4.75% by weight of nickel oxide grey
11.75% by weight of zinc oxide, French process
33.50% by weight of iron oxide (red), tech. grade

The first batch (MF-141-L) weighed 5 kg, the second (MF-141-H weighed 4.6 kg; 6500 ccm of water was added to the L-batch, 6000 ccm to the H-batch. Both batches were milled for 15 hours (over night).

After drying and breaking up the cakes, the material was worked in a Lancaster mixer with 1% (of the weight of dry material) of Polyvinyl alcohol dissolved in sufficient water to form a paste. One part of each body was screened through 20 mesh only, thus containing all grain sizes from 20 mesh down to fine dust; from another part of each body, the dust was taken out by an 80-mesh screen. Then 6% water was added to the granulated body.

Instead of pressing samples with three different pressures, this time only 5 tons and 10 tons have been applied. A pressure of 15 tons is too high with respect to the die-size (toroid F-109) and there were signs of overstressing the die. Since overpressing as well as underpressing has to be avoided in any case of practical production, there was no point in jeopardizing the die by applying excessive pressure. Thus, there were a total of eight variations to be fired.

With respect to the firing, there was a difference of procedure compared with the MF-254-"G" body work previously done. For the MF-141-"I"-body series, a medium size, gas-fired, car-type, tunnel oven with a firing cycle of 16 hours has been used. The slabs loaded with the toroidal cores were located on the middle level of the cars. There were 40 cores on each slab. Of all the kilns available, this kiln is the most reliable to handle medium size production lots. The peak temperature was 2360°F (almost cone 12 down).

PART II (Cont'd.)

The total number of cores in this uniformity test was about 400. These were tested according to the standard procedure for μ_o at 1 Mcs and the measurements were corrected for temperature deviations from an ambient of 27°C. Since the test frequency was rather high for "I"-141 material due to the high losses, these rings will be retested at about 100 Kcs for μ_r and μ_o . This lower frequency is close to that of the field of application of this ferrite and any changes in the distributions as a function of frequency may be noticeable.

The test results are shown in Table LV and Graphs 174 and 175. Table LV indicates that the best results for uniformity of μ_o (1 Mcs) are obtained using a low temperature calcine in all comparable cases of particle size and pressure.* In the low-fired calcine preparation particularly, the 20 mesh granulation (i.e., the dust not removed) gives very good results at both the 10-ton and 5-ton pressures. Apparently when using the low-fired calcine any removal of the dust (through 20 mesh and on 80 mesh) reduces the uniformity. However, for the high-fired calcine preparation, there appears to be little change of the overall uniformity as a function of either the particle size or pressure.

It can be seen by comparing the distribution curves (Graphs 174 and 175) that the best conditions for uniformity (low fired calcine, through 20 mesh at pressure of either 5 tons or 10 tons) also results in the highest μ_o values by about 5% (using the peak of each distribution as an average indication of μ_o). Also, it is interesting to note that irrespective of calcine preparation, the 20 mesh granulation gives about equal μ_o values at each pressure while in the other granulation where the dust is removed the permeability shifts to lower values when the pressure is reduced.

Although at 1 Mcs the losses in this ferrite are very high and all the Q values are in the order of 2, the low-fired calcine preparation in each case yielded higher Q's. This small difference in losses at 1 Mcs may be magnified at 100 Kc.

*The pressures in psi reported in the two previous reports were in error. Actually, 3120 psi, 2080 psi and 1040 psi were respectively 15 tons, 10 tons and 5 tons hydraulic ram pressure on the F-109 die. (O.D. = 1.00" I.D. = .625")

PART II (Cont'd.)

The conclusions that can be drawn from this experiment and this particular firing temperature for MF-141 "I" body are:

- a) the low-fired calcine preparation yields optimum results for uniformity of μ_0 , and magnitudes of μ_0 and Q.
- b) removal of the dust yields poorer results in magnitude and uniformity of μ_0 when using the optimum condition of low-fired calcine.
- c) a marked increase in sensitivity to pressure variations occurs when the dust is removed using either calcine preparation.

Dimensional uniformity has still to be measured on these toroids. These results and many others of other magnetic properties will be reported in the future.

Another result of this uniformity test is that the conditions for test results (μ_0 at 1 Mcs) are different from those of the MF-254 "G" body.

PART III

RESEARCH PLANNED FOR THE NEXT QUARTER

- 1) More information will be given on low-loss low-permeability body Ferramic "Q"
- 2) Investigation of Mn-Zn ferrites will be resumed. Special emphasis will be put on low-frequency measurements.
- 3) The Reproducibility and Uniformity test will be carried on. Information on the uniformity of MF-141-"I" will be evaluated for other magnetic properties.

MANHOURS SPENT ON CONTRACT FOR THE PERIOD OF
October 1, 1953 to December 31, 1953

NAME	TITLE	HOURS
Dr. E. Albers-Schoenberg	Supervisor	130
Ephraim Gelbard	Project Engineer	126
Dr. K. Wetzel	Ceramist	136
M. Eisenberg	Electrical Engineer	184
S. Ortepico	Ceramist	93
James Callahan	Ceramist	481
S. Golion	Technician	121
J. Kurtz	Technician	114
C. Purzas	Technician	104
W. Hegedus	Technician	91
A. Koseski	Technician	99
Mary Horton	Meas. Technician	319
Ruth Mainwright	Meas. Technician	204

PROPERTIES OF NEW "B"-BODY TYPE COMPOSITIONS

	Fluxes	Firing Facility	Firing Temp.	Magnetic Properties				Temp. Coeff. of μ_0 $\frac{\Delta \mu_0}{\mu_0}$
				μ_0 (1 Mcs)	μ_{max}	Bs	$\frac{Q}{f}$ (1 Mcs)	
1835-A	CaF ₂ SiO ₂	Large production tunnel kiln	2285°F	90	190	2100	90	-1.0 (30-100°C)
1835-B	CaF ₂ SiO ₂	Small production tunnel kiln	2330°F	87	176	2100	86	+3.5 (30-100°C)
1835-D	CaCO ₃ SiO ₂	Large production tunnel kiln	2285°F	88	---	---	81	+2.0 (30-100°C)

TABLE LIII

COMPARISON OF MAGNETIC PROPERTIES OF FERRAMIC Q
 (PRELIMINARY DATA) WITH TWO OTHER LOW LOSS FERRITES

	Ferramic Q	Ferramic N-874	Ferramic J-472
μ_0 (1 Mcs)	125	200	330
Q (1 Mcs)	≥ 400	120	61
$\frac{1}{\mu_0 Q}$ (1 Mcs)	≤ 0.00002	0.00004	0.00005
Curie Temp. ($^{\circ}\text{C}$)	> 250	290	180
$\frac{\Delta \mu_0}{\mu_0}$ ($\% / ^{\circ}\text{C} - 1 \text{ Mcs}$) ($25^{\circ}\text{C} - 100^{\circ}\text{C}$)	+0.10	+0.14	+0.22
Bs (Gauss-HDC=25) oersteds	2900	3000	2900
BR (Gauss)	1300	2300	1600
Hc (oersted)	1.80	0.50	0.80
μ_{max}	400	500	750

TABLE LIV

COMPARISON OF μ_0 AND Q BY VARIOUS MEASUREMENT METHODS
(1 Mcs) (F-268 Toroid)

ECCT	R.F. Bridge μ_0	(916A)**** Q*	Boonton Q Meter (290A) μ_0	Q*	R, F. Permeameter (Size B)*** μ_0	Q*
A-106	20.1	139.3	20.4	115**	19.3	192.0
B-90	74.5	72.9	75.6	60	65.8	75.0
C-159	240.7	52.8	243	50	215	52.0
D-216	350.9	39.9	353	37.5	321	39.0
E-174	632.3	10.6	652	11	625	11.9
F-254	354.2	21.6	364	21	312	23.5
G-119	715.2	4.6	762	<10	622	5.85
H-1102	599.4	3.6	744	<10	622	4.44
I-141	825.9	2.1	948	<10	1276	1.57
J-172	289.6	59.8	294	56	278	63.7
K-974	188.2	90.1	187	80	180	106
L-1676	906.2	4.3	948	<10	831	4.25

$$Q_m = \frac{1}{\tan \delta} \frac{1}{m}$$

** Low Q mica parallel condenser

*** Co, Qc established with parallel air condenser

**** E_m less than 0.45 millivolts

TABLE LV

DISTRIBUTION OF μ_0 (1 Mcs) MF 141-"I" AT 27°C FOR TWO CALCINES
 TWO DIFFERENT PARTICLE SIZES, AND TWO DIFFERENT PRESSURES
 DIE F 109 - (PERCENTAGES OF CORES WITHIN $\pm 2\text{-}1/2\%$ and $\pm 5\%$ FOR μ_0
 USING THE PEAK OF THE DISTRIBUTION CURVES AS THE CENTER VALUE)


CALCINING PREPARATION	PRESSING PRESSURE	THROUGH 20 MESH		THROUGH 20 MESH ON 80 MESH	
		WITHIN $\pm 2\text{-}1/2\%$	WITHIN $\pm 5\%$	WITHIN $\pm 2\text{-}1/2\%$	WITHIN $\pm 5\%$
L Preparation (Low Fired Calcine)	10 Tons	98.0%	100.0%	84.0%	100.0%
	5 Tons	94.1%	98.0%	72.0%	92.0%
H Preparation (High Fired Calcine)	10 Tons	68.6%	98.0%	77.1%	93.8%
	5 Tons	70.6%	98.0%	77.5%	96.2%

GENERAL CERAMICS & STEATITE CORPORATION

GRAPH 172

12-15-53


INITIAL PERMEABILITY (1. No. 1) vs. TEMPERATURE FOR MF 1835 A, B & D

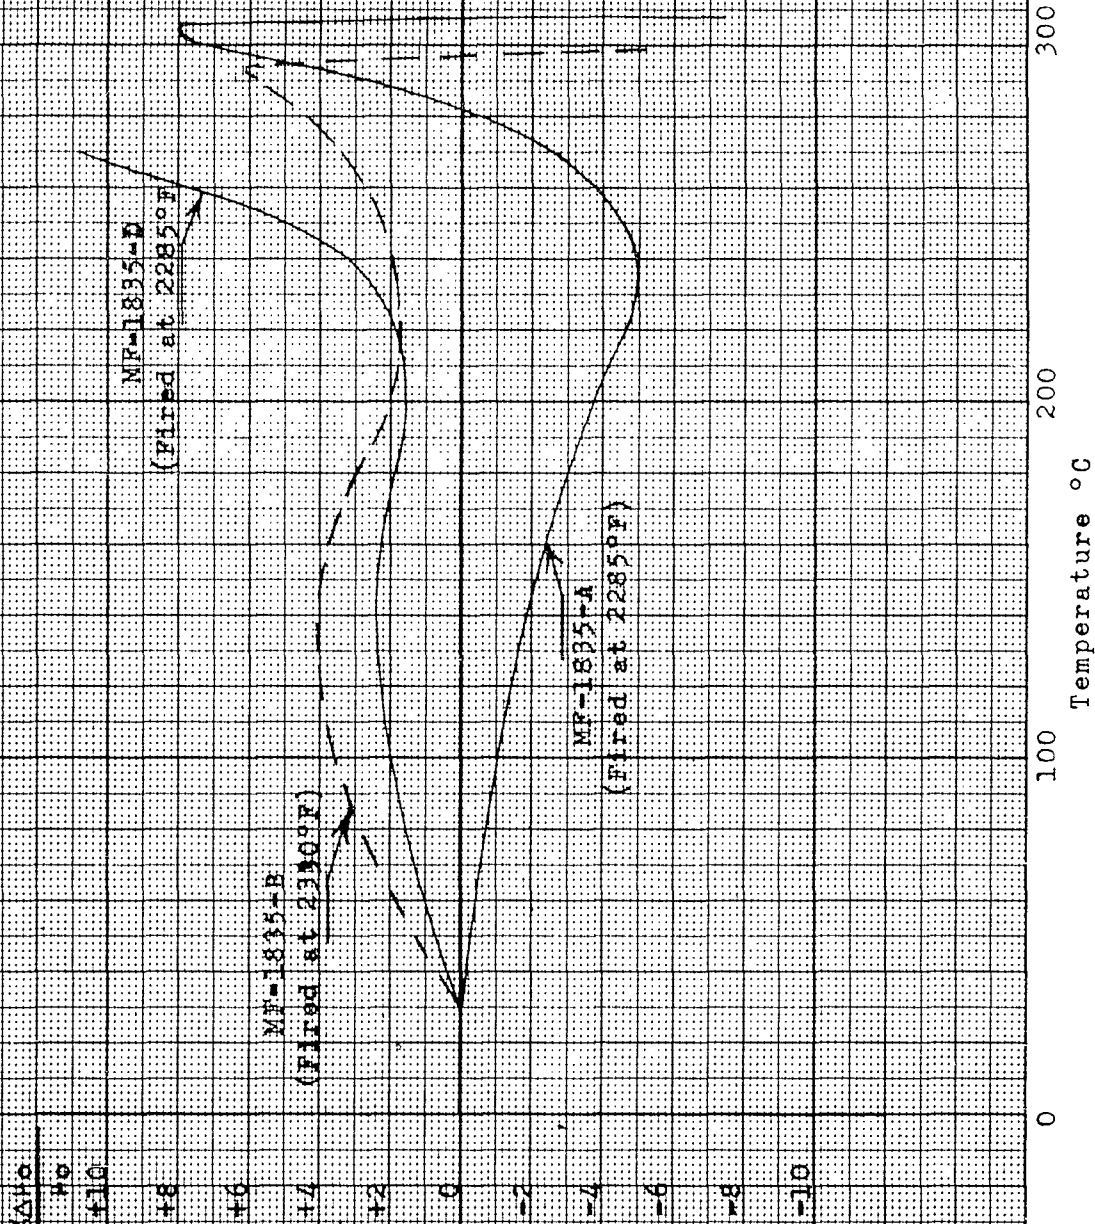

12-10-53

GRAPH 173

INITIAL PERMEABILITY (1 Mos) vs. TEMPERATURE FOR MF 1835-B AT THREE FIRING TEMPERATURES

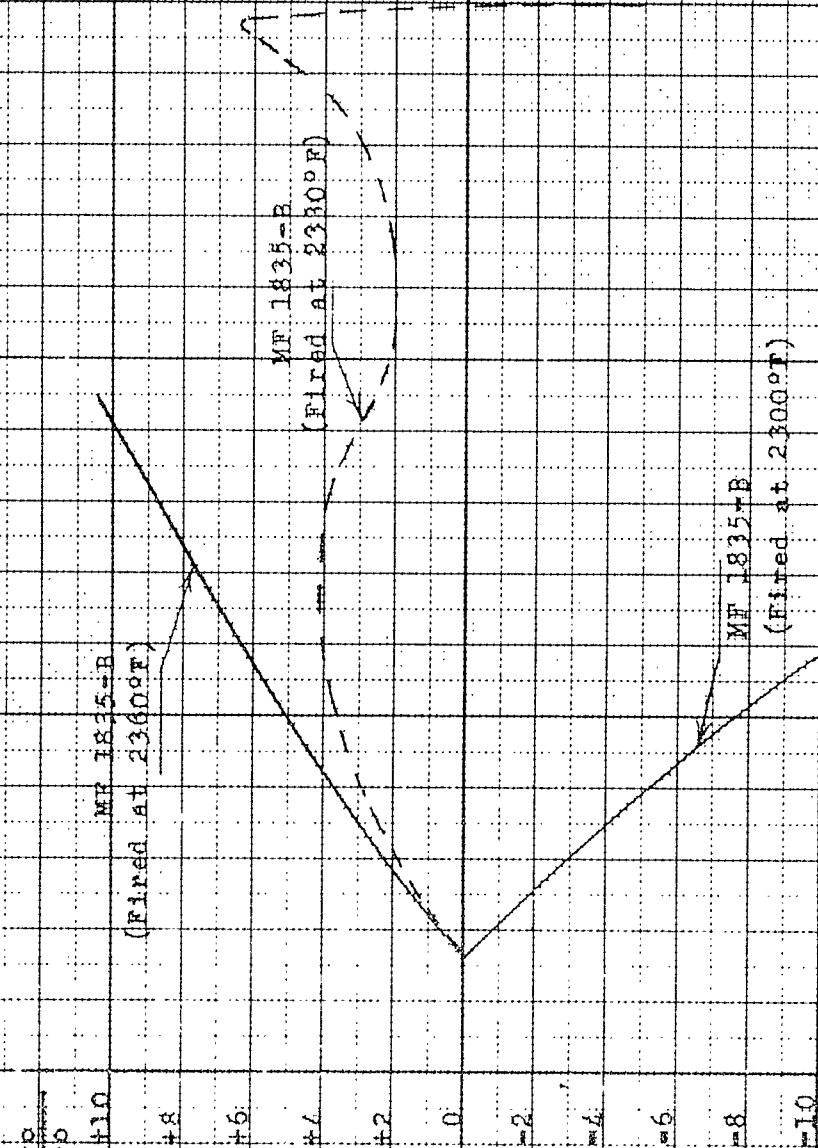


GENERAL CERAMICS & STEATITE CORP.

GRAPH 174

12-10-53

DISTRIBUTION OF P₀ (1 MCS) OF MP 141 WIM BODY AT 279°C
TWO DIFFERENT PARTICLE SIZES, TWO DIFFERENT PRESSURES
A PREPARATION (LOW FIRED CALCINE) DIE F 109

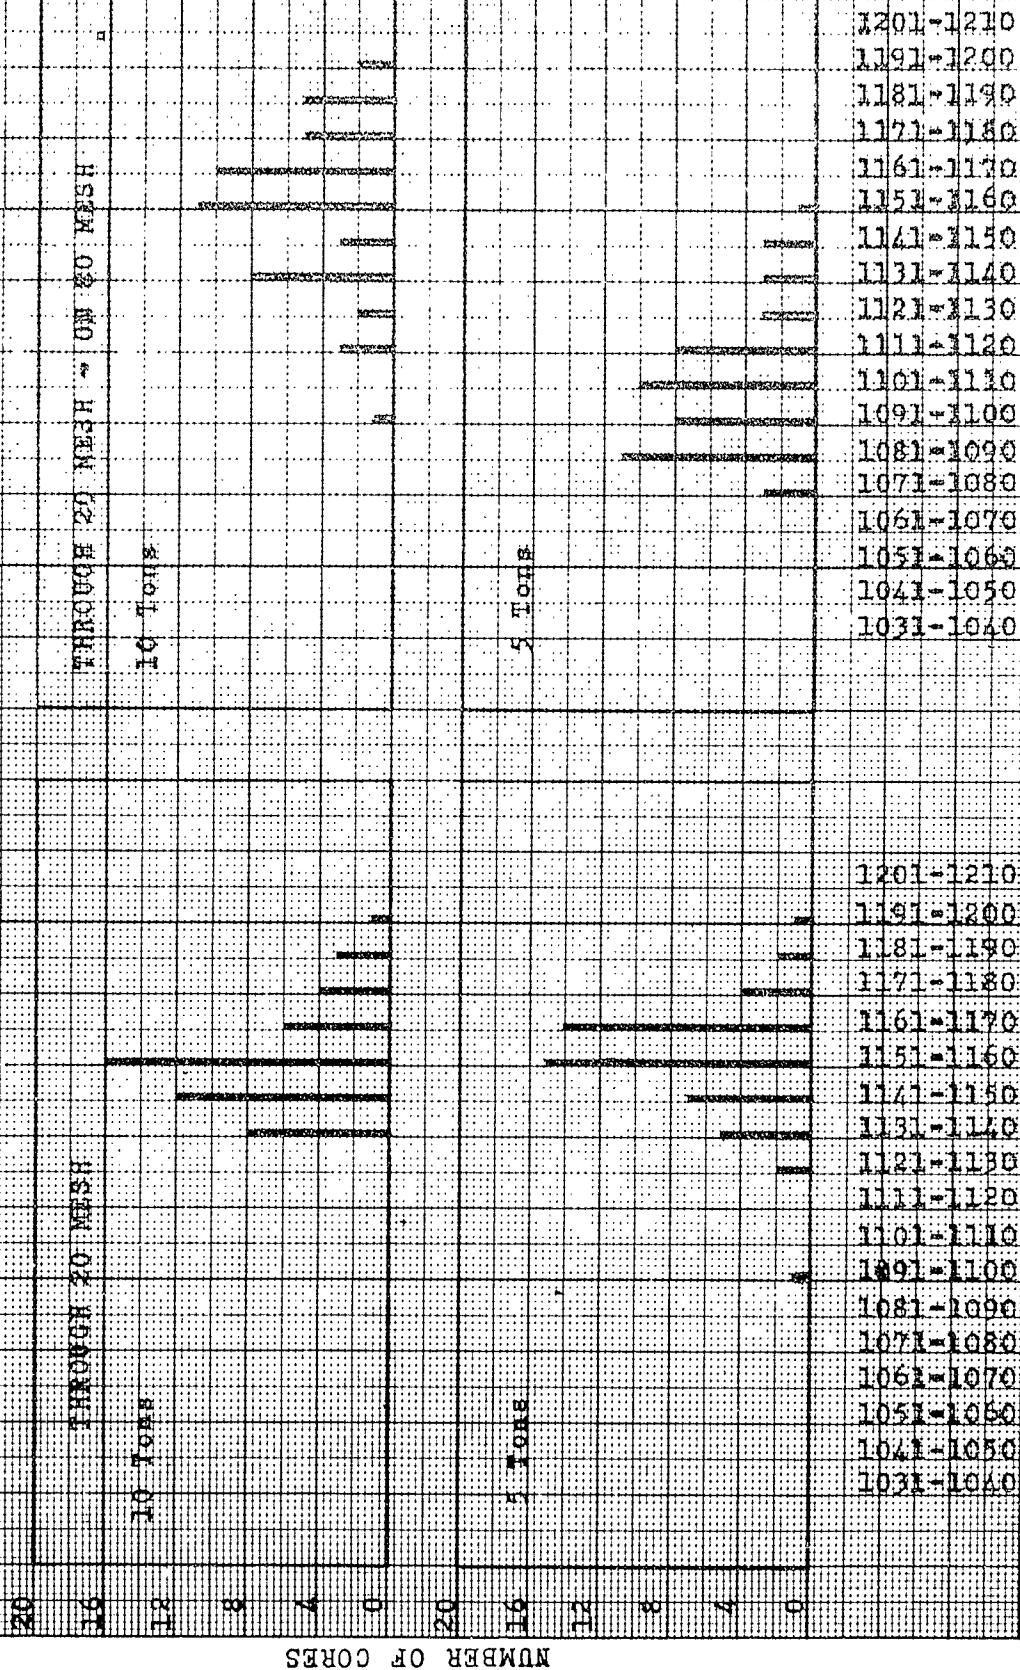

12-15-53

GRAPH 175

GENERAL CERAMICS & STEATITE CORP.

DISTRIBUTION OF NO. (1 Mes) OF MF 141 "1" BODY AT 2700
TWO DIFFERENT PARTICLE SIZES, TWO DIFFERENT PRESSURES
H PREPARATION (HIGH FIRED CALCINE) DIE F 109

THROUGH 20 MESH

THROUGH 20 MESH - ON 80 MESH

10 Tons

10 Tons

5 Tons

5 Tons

1201-1210
1191-1200
1181-1190
1171-1180
1161-1170
1151-1160
1141-1150
1131-1140
1121-1130
1111-1120
1101-1110
1091-1100
1081-1090
1071-1080
1061-1070
1051-1060
1041-1050
1031-1040

1201-1210
1191-1200
1181-1190
1171-1180
1161-1170
1151-1160
1141-1150
1131-1140
1121-1130
1111-1120
1101-1110
1091-1100
1081-1090
1071-1080
1061-1070
1051-1060
1041-1050
1031-1040

NUMBER OF CORES