

UNCLASSIFIED

AD NUMBER	
AD153035	
CLASSIFICATION CHANGES	
TO:	UNCLASSIFIED
FROM:	CONFIDENTIAL
LIMITATION CHANGES	
TO: Approved for public release; distribution is unlimited. Document partially illegible.	
FROM: Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative/Operational Use; FEB 1958. Other requests shall be referred to Frankford Arsenal, Philadelphia, PA. Document partially illegible.	
AUTHORITY	
ARRADCOM ltr 17 Nov 1979 ; ARRADCOM ltr 17 Nov 1979	

THIS PAGE IS UNCLASSIFIED

153 035

UNCLASSIFIED

AD 153 035

CLASSIFICATION CHANGED
TO: UNCLASSIFIED
FROM: CONFIDENTIAL
AUTHORITY:

ARRA DCOM 100

19 NOV 79



UNCLASSIFIED

AD 153035

Armed Services Technical Information Agency

**ARLINGTON HALL STATION
ARLINGTON 12 VIRGINIA**

**FOR
MICRO-CARD
CONTROL ONLY**

1 OF 1

NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY OTHER PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.

CONFIDENTIAL

FRANKFORD ARSENAL

REPORT No. R-1436

COPY No. 28



PERFORATING ABILITY OF ARROW-TYPE PROJECTILES EFFECT OF PROJECTILE LENGTH (U)

G. W. CURTIS

J. R. KIMER

H. E. FITZINGER

February 1958

OCO Project No. TA1-5002
DA Project No. 5104-01-001

This document contains information affecting the national defense of the United States within the meaning of the Espionage Laws, Title 18, U.S.C. Sections 793 and 794. The transmission or the revelation of its contents in any manner to an unauthorized person is prohibited by law.

58 AA 2368

Pitman-Dunn Laboratories Group,
FRANKFORD ARSENAL
Philadelphia 37, Pa.

(CODE SHEET INCLOSED)

CONFIDENTIAL

DEGRADING DATA CANNOT BE PREDETERMINED

NSA 1 & 2

AD No. 153035
ASTIA FILE COPY

AD No. 153035
ASTIA FILE COPY

This document is the property of the United States
Government. It is furnished for the duration of the contract and
shall be returned when no longer required, or upon
recall by ASTIA to the following address:
Armed Services Technical Information Agency, Arlington Hall Station,
Arlington 12, Virginia

**NOTICE: THIS DOCUMENT CONTAINS INFORMATION AFFECTING THE
NATIONAL DEFENSE OF THE UNITED STATES WITHIN THE MEANING
OF THE ESPIONAGE LAWS, TITLE 18, U.S.C., SECTIONS 793 and 794.
THE TRANSMISSION OF THE REVELATION OF ITS CONTENTS IN
ANY MANNER TO AN UNAUTHORIZED PERSON IS PROHIBITED BY LAW.**

BEST

AVAILABLE

COPY

THE
NG
4.

LAW.

CONFIDENTIAL

REPORT No. R-1436

Copy No. 28

PERFORATING ABILITY OF ARROW-TYPE PROJECTILES:
EFFECT OF PROJECTILE LENGTH (U)

February 1958

OCO Project No. TA1-5002
DA Project No. 5A04-01-001

Prepared by

C. W. CURTIS
Consultant

J. R. Kimer
J. R. KIMER
Physicist

H. E. Fatzinger
H. E. FATZINGER
Chief, Penetration Mechanics Section

Reviewed by

G. C. WHITE, JR.
Chief
General Physics Branch

E. R. THILO
Director
Physics Research Laboratory

Approved by

C. C. Fawcett
C. C. FAWCETT
Director
Pitman-Dunn Laboratories Group

For

JAMES A. RICHARDSON, III
Brigadier General, USA
Commanding

This document contains information affecting the national defense of the United States within the meaning of the Espionage Laws, Title 18, U.S.C. Sections 793 and 794. The transmission or the revelation of its contents in any manner to an unauthorized person is prohibited by law.

Reproduction of this document, in whole or in part, is prohibited except with permission of the issuing office; however, ASTIA is authorized to reproduce the document for United States governmental purposes.

FRANKFORD ARSENAL
Pitman-Dunn Laboratories Group
Philadelphia 37, Pa.

CONFIDENTIAL
REGRADE DATA CANNOT BE PREDETERMINED

CONFIDENTIAL

TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION	1
PROJECTILE DIMENSIONS AND CONDITIONS OF IMPACT	1
RESULTS	2
Terminal Ballistic Data	2
Effect of Projectile Length	2
Derivation of Perforation Formula	2
Perforation Formula for Full Caliber Projectiles	8
CONCLUSIONS	8
WORK IN PROGRESS	10
APPENDIX	11
Projectile Design	11
Penetrators	11
Stabilizers	11
Sabots	17
Launching Devices	17
Guns	17
Chambers	21
Instrumentation	24
Velocity	24
Shadowphotography	24
High-speed Radiography	24
DISTRIBUTION	28

CONFIDENTIAL

CONFIDENTIAL

OBJECT

To investigate the effect of projectile length on the perforating ability of arrow-type projectiles.

SUMMARY

Tests have been carried out to determine the effect of projectile length on the perforating ability of small caliber arrow-type projectiles fired against rolled homogeneous armor at 60° obliquity. The tests included projectiles from 3.0 to 16.7 calibers long and targets from 1.11 to 4.75 calibers thick. The projectiles were made of hardened steel and had diameters of 0.263 in. to 0.450 in.

At this large angle of attack and for projectiles of a given diameter, the energy required for perforation increases with increase in projectile length for all plate thicknesses tested.

An equation has been developed which relates projectile length, as well as the usual projectile and plate parameters, to the energy required to defeat a target. Although this equation is empirical, it predicts to a reasonable accuracy the observed effects due to changes in the various parameters and should, therefore, be useful for purposes of projectile design. With the adjustment of certain constants from limited firing data, the equation should be applicable to large as well as small caliber arrow-type projectiles.

AUTHORIZATION

Ltr, Picatinny Arsenal, ORDBB-TE3, 471.14/G-281, 26 July 1955

CONFIDENTIAL

CONFIDENTIAL

INTRODUCTION

With the development of fin stabilization it has become possible to fire very long projectiles with the consequent benefits of high caliber density. Two of these benefits are: less retardation in flight and a greater concentration of energy into a small area of the target plate. Also, compared to spin-stabilized subcaliber projectiles, a greater ratio of core to carrier weight can be obtained. The result has been the development of effective arrow-type projectiles.

For a fin-stabilized arrow-type projectile, there is no effective limit to the length set by the exterior ballistic performance. On the other hand, the length would be limited by the terminal ballistic performance if there were serious deterioration as the length increased. Thus a correlation between projectile length and perforating ability becomes an important factor. Previously, no notable correlation between these quantities had been established, probably because so little variation in length is possible with a spin-stabilized projectile. Long projectiles cannot be stabilized by spinning. This correlation and the possible deterioration of terminal ballistic performance with length are the subject of the present report.

Only firings at 60° obliquity are considered.

PROJECTILE DIMENSIONS AND CONDITIONS OF IMPACT

The variables investigated, together with their respective symbols, follow.

- l - Projectile length - 1.35 in. to 5 in.
- d - Projectile diameter - 0.263 in. to 0.450 in.
- l/d - Projectile length to diameter ratio - 3.0 to 16.7
- t - Plate thickness - 1/2 in. to 1 1/4 in.
- t/d - Thickness to diameter ratio - 1.11 to 4.75
- Angle of attack - 60° (90/40 mm results - 55° and 60°)

A description of the various experimental projectiles, together with their launching and flight characteristics, is included in the Appendix.

CONFIDENTIAL

RESULTS

Terminal Ballistic Data

A summary of the ballistic results is given in Table I. This Table includes the various parameters listed above, together with the protection ballistic limits (PBL's) and specific limit energies (SLE's). A discussion and correlation of the results are contained in the following two sections. All plates were rolled homogeneous armor of 280-320 Bhn.

Effect of Projectile Length

Firing results for three l/d ratio groups are shown in Figure 1, where the logarithm of the SLE is plotted against the logarithm of the caliber plate thickness (t/d). It can be seen in Figure 1 that the SLE for constant t/d , required to defeat the target, is inversely proportional to the projectile length. Hence, the shorter projectiles are more efficient penetrators than the longer ones. The curves for a given l/d ratio are not parallel, but seem to have less separation at larger t/d 's. Because the plot is logarithmic, this means that the fractional increase in SLE due to a given increase in projectile length becomes less as the t/d ratio becomes greater. Also, since the plots are not straight lines, the SLE is not directly proportional to a power of t/d .

Derivation of Perforation Formula

No simple perforation formula has been found which represents these data correctly in all details. However, the following equation takes into account the main variations.

$$SLE = \frac{WV_L^2}{d^3} = \frac{W^*V_L^2}{d^3} \left[1 + c \left(\frac{l}{t} \right)^n \right] = a \left[\frac{t}{d} - b \right] \left[1 + c \left(\frac{l}{t} \right)^n \right] \quad (1)$$

All the variables of this equation are defined in the notes of Table I except W^* and the constants: a , b , c , and n . W^* is defined by

$$W^* = \frac{W}{1 + c \left(\frac{l}{t} \right)^n}$$

CONFIDENTIAL

Table I. Summary of Arrow-type Projectile Data

d - Projectile diameter (in.)
 - Projectile length (in.)
 W - Projectile weight (lb)
 t - Plate thickness (in.)
 V_L - Protection ballistic limit* of plate (f/s)
 SLE - Specific limit energy** = WV_L^2/d^3 (lb ft²/in.³ sec² x 10⁶)

Projectile No.	Figure Symbol***	d	/d	W/d	Plate thickness (in.)	t/d	l/t	V_L	SLE
36		0.450	3.0	0.556	1/2 3/4	1.11 1.67	2.70 1.80	3630 5950	7.3 19.7
37	X	0.375	4.9	0.962	1/2 3/4	1.33 2.00	3.60 2.45	3710 5250	13.3 26.6
19	+	0.312	6.4	1.222	1/2 3/4 1	1.60 2.40 3.20	4.00 2.67 2.00	4150 5700 6300	21.3 39.6 48.4
38		0.300	9.0	1.878	1/2 3/4 1	1.67 2.50 3.33	5.39 3.60 2.70	3550 4530 5575	23.6 38.5 58.2
16		0.312	9.6	1.952	1/2 3/4 1 1 1/8	1.60 2.40 3.20 3.60	6.00 3.40 3.00 2.67	3335 4300 5635 5570	21.7 33.2 62.0 60.7
33		0.300	10.0	2.033	3/4 1 1 1/4	2.50 3.33 4.17	4.00 3.00 2.40	4350 5150 5780	38.4 54.0 67.9
14		0.312	12.8	2.654	1	3.20	4.00	4860	62.6
39		0.263	13.2	2.786	1/2 3/4 1 1 1/4	1.9 2.85 3.80 4.75	6.94 4.63 3.47 2.78	3500 4600 5150 5100	34.2 59.2 74.0 62.4
34		0.300	13.3	2.763	3/4 1 1/4	2.50 4.17	5.32 3.20	4200 5275	48.8 77.0
15		0.312	16.0	3.385	3/4 1	2.40 3.20	6.66 5.00	4025 4400	54.9 65.6
35		0.300	16.7	3.478	1/2 1 1/4	1.67 4.17	10.0 4.00	3150 4650	34.5 75.2

*A protection-complete penetration is obtained whenever a fragment or fragments of either the impacting projectile or the plate are ejected from the rear of the plate with sufficient energy to perforate a thin, mild steel plate (about 0.020 in.) or equivalent screen placed parallel to and approximately six inches rearward of the plate.

**The specific limit energy is the kinetic energy of the projectile divided by the cube of its diameter.

***These symbols are used in Figures 1 through 4.

CONFIDENTIAL

36.231.35298/ORD.57
R-1436

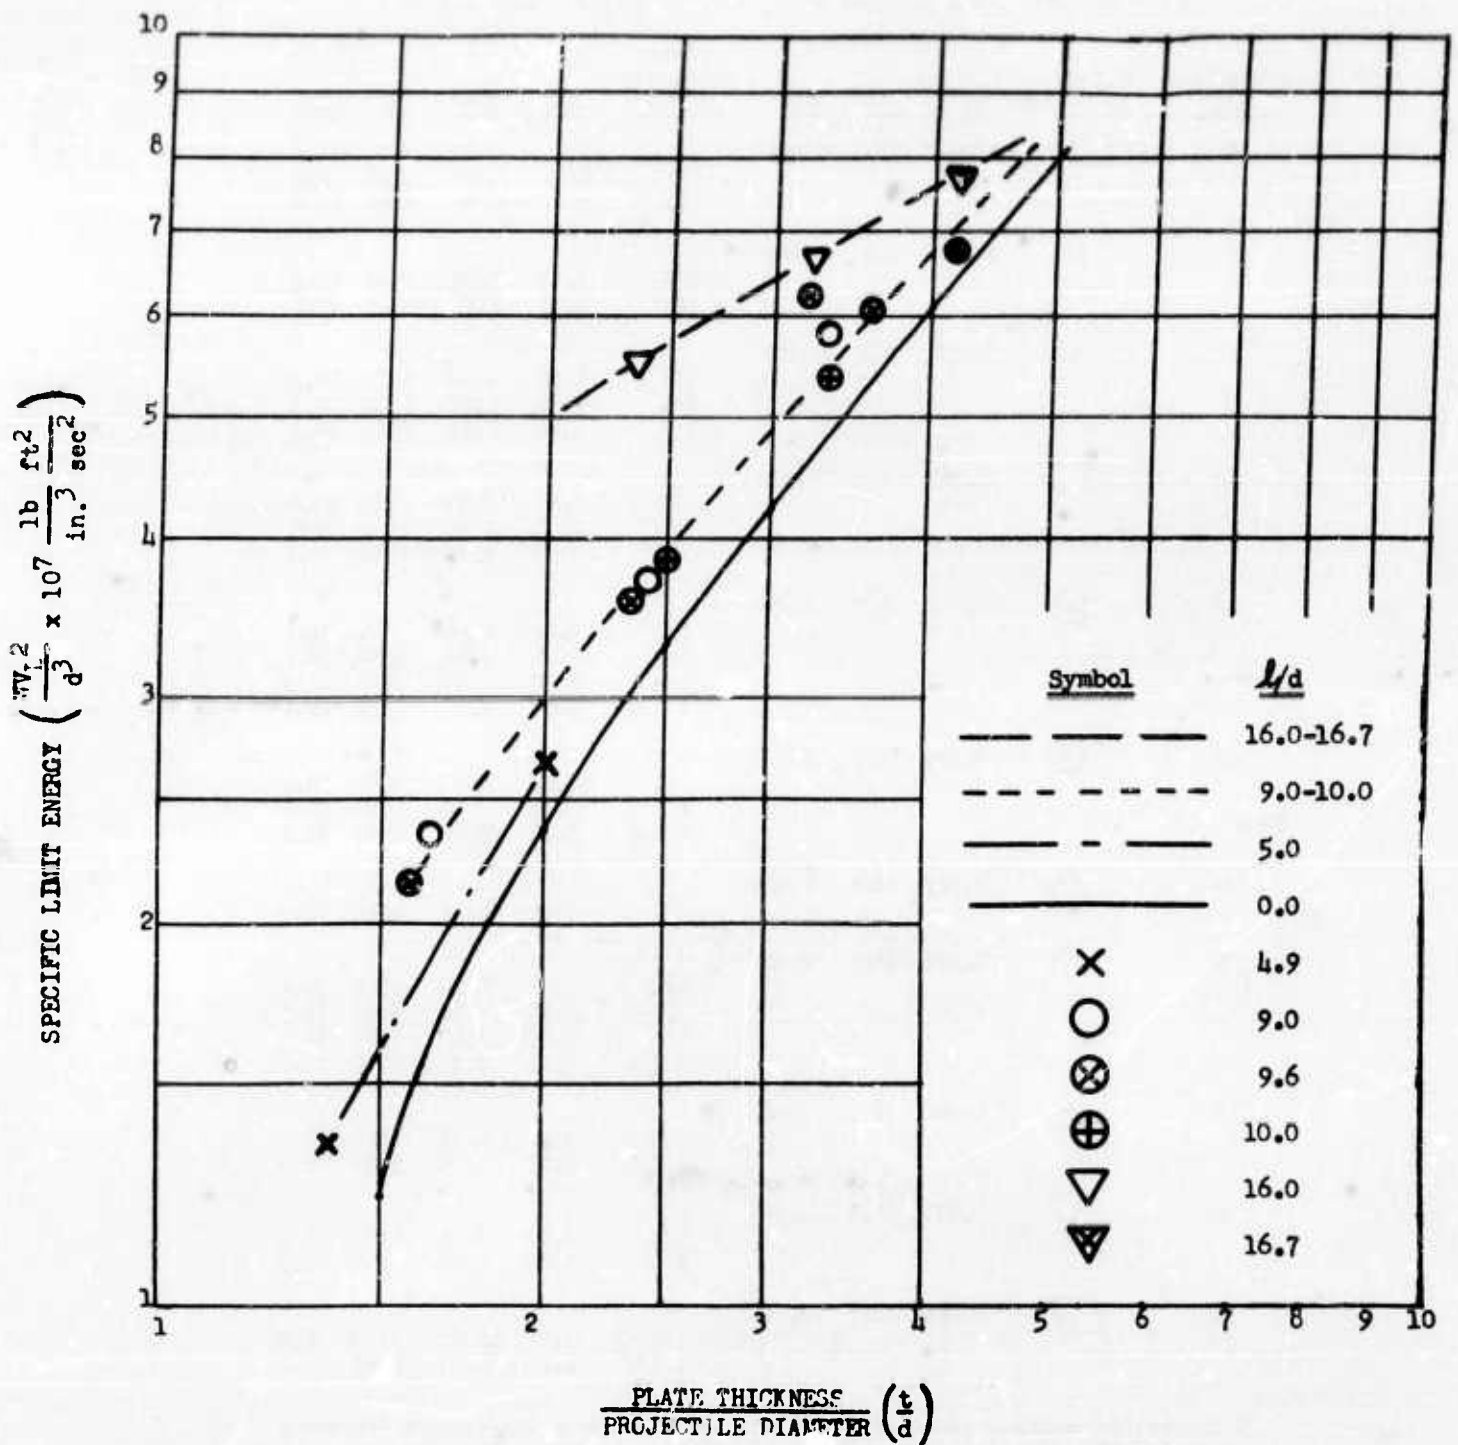


Figure 1. Effect of projectile length on penetrating ability of arrow-type monobloc steel projectiles vs RH armor at 60° obliquity

CONFIDENTIAL

CONFIDENTIAL

and may be considered as that fraction of the projectile mass which is effective in perforating the plate. The constants a , b , c , and n are determined from the ballistic data.

It will be noted that this equation leads to the same types of variation for the perforation limits as described in the last section. Thus, with $\ell = 0$, WV_L^2/d^3 vs t/d on a log-log plot would be a curved line with a slope approaching unity for large t/d . Also, the effect of increasing ℓ is to increase SLE above the value given by $a[t/d-b]$, but this effect becomes less with increasing t .

Figure 2 shows all perforation data, together with curves derived from equation (1) with $a = 1.86 \times 10^7$, $b = 0.73$, $c = 0.015$, and $n = 2$. The values for a and b were determined from the solid lines drawn in Figures 1 and 2 as an estimate of the penetration curve for $\ell = 0$.

Equation (1) may be rewritten as

$$\frac{\frac{WV_L^2}{d^3} - \frac{W^*V_L^2}{d^3}}{\frac{W^*V_L^2}{d^3}} = c \left(\frac{\ell}{t} \right)^n \quad (2)$$

Therefore c and n can, in principle, be determined from a plot on log-log paper of the left hand side of equation (2) vs ℓ/t . Such a plot is shown in Figure 3. If equation (1) were exactly true, if the values for a and b were correct, and if there were no scatter in the data, a plot of the data would result in a straight line. From this graph, c and n were given values of 0.015 and 2, respectively.

Figure 4, which is a plot of the SLE's adjusted to $\ell = 0$, shows how much the spread in data has been reduced. In this figure the SLE, WV_L^2/d^3 , is adjusted by dividing by $(\ell + 0.015 [\ell/t]^2)$, which is the length-dependent term in equation (1). However, it may be noted that the adjusted values are still too high in the range for $t/d = 3$ to 4. Furthermore, it does not account for the curvature of the plots in Figures 1 and 2.

36.231.35299/ORD.57
R-1436

CONFIDENTIAL

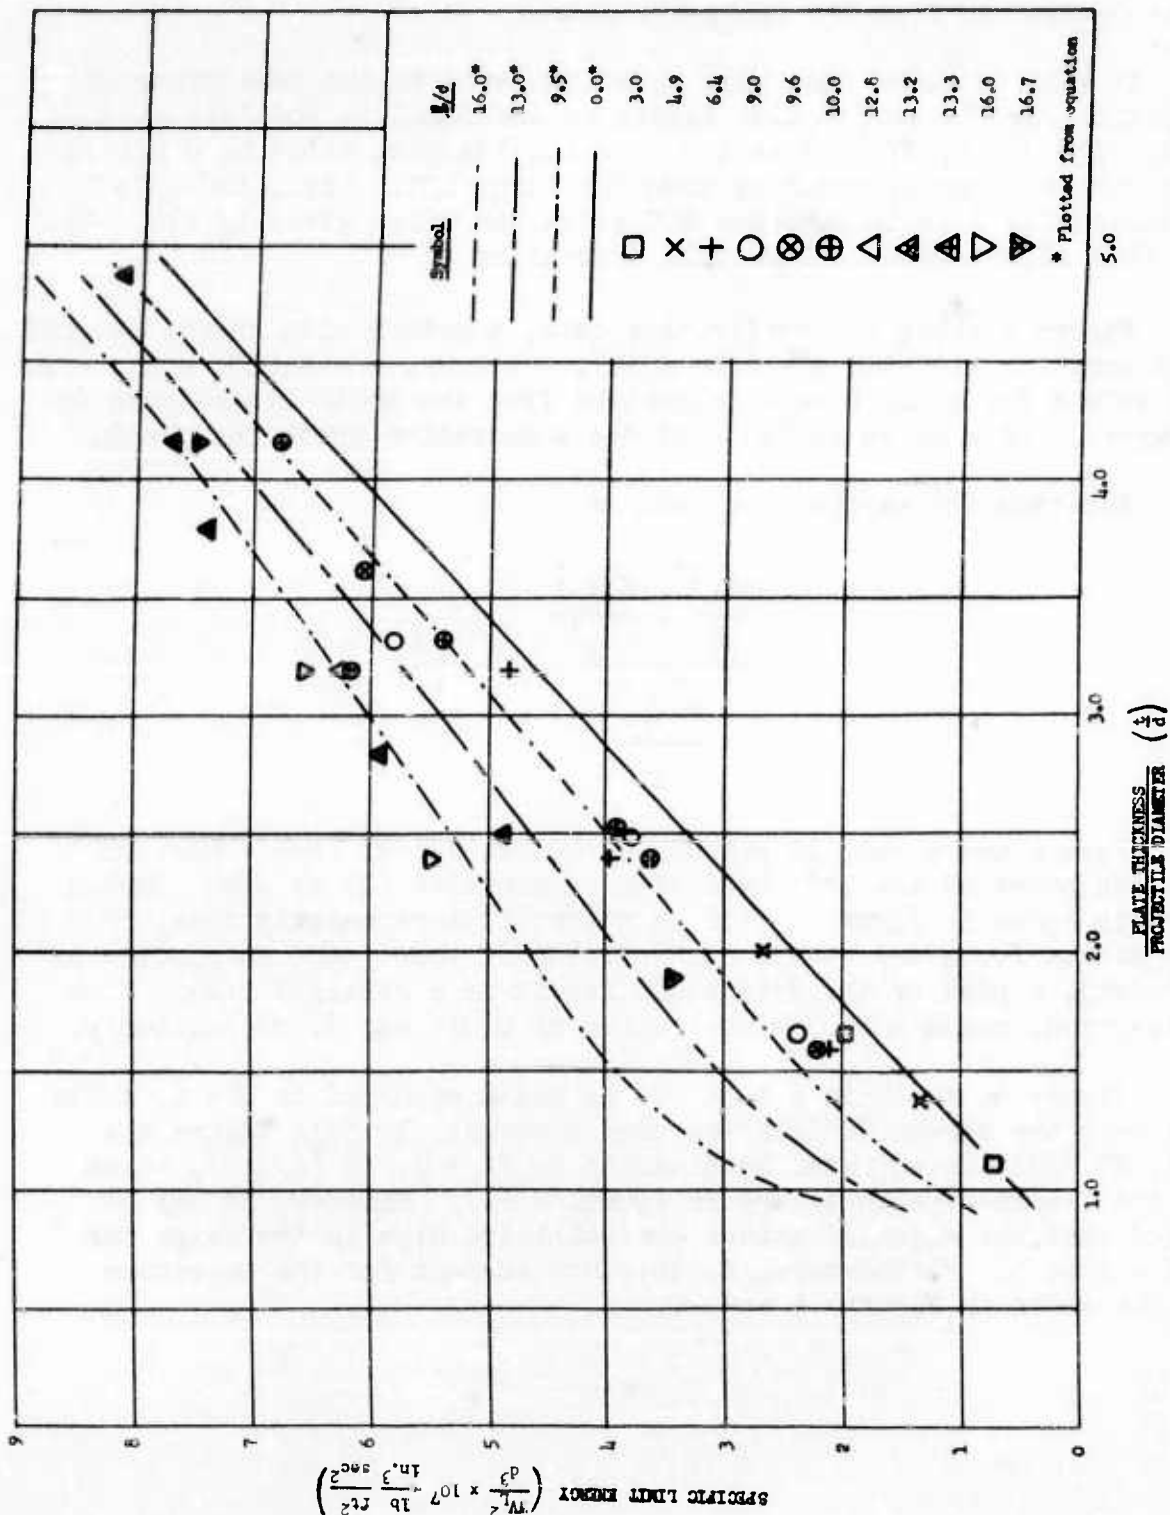


Figure 2. Perforation energy vs plate thickness for arrow-type monobloc steel projectiles of various lengths at 60° obliquity

CONFIDENTIAL

36.231.35300/ORD.57
R-1436

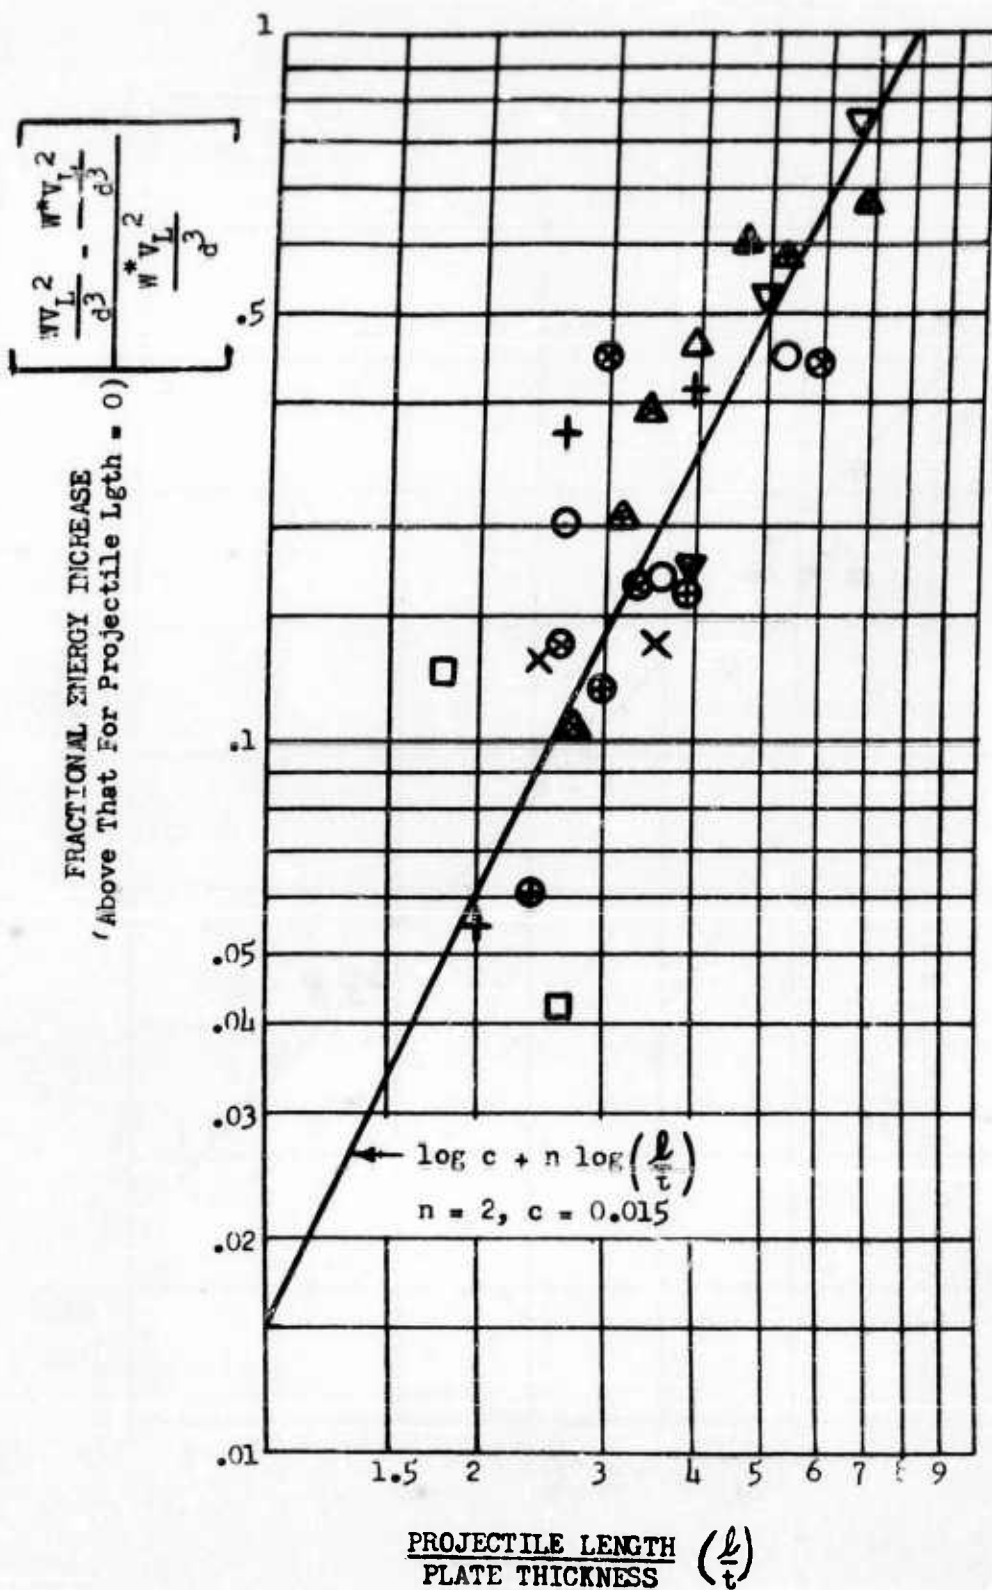


Figure 3. Correction for perforation energy due to projectile length

CONFIDENTIAL

36.231.35301/ORD.57
R-1436

CONFIDENTIAL

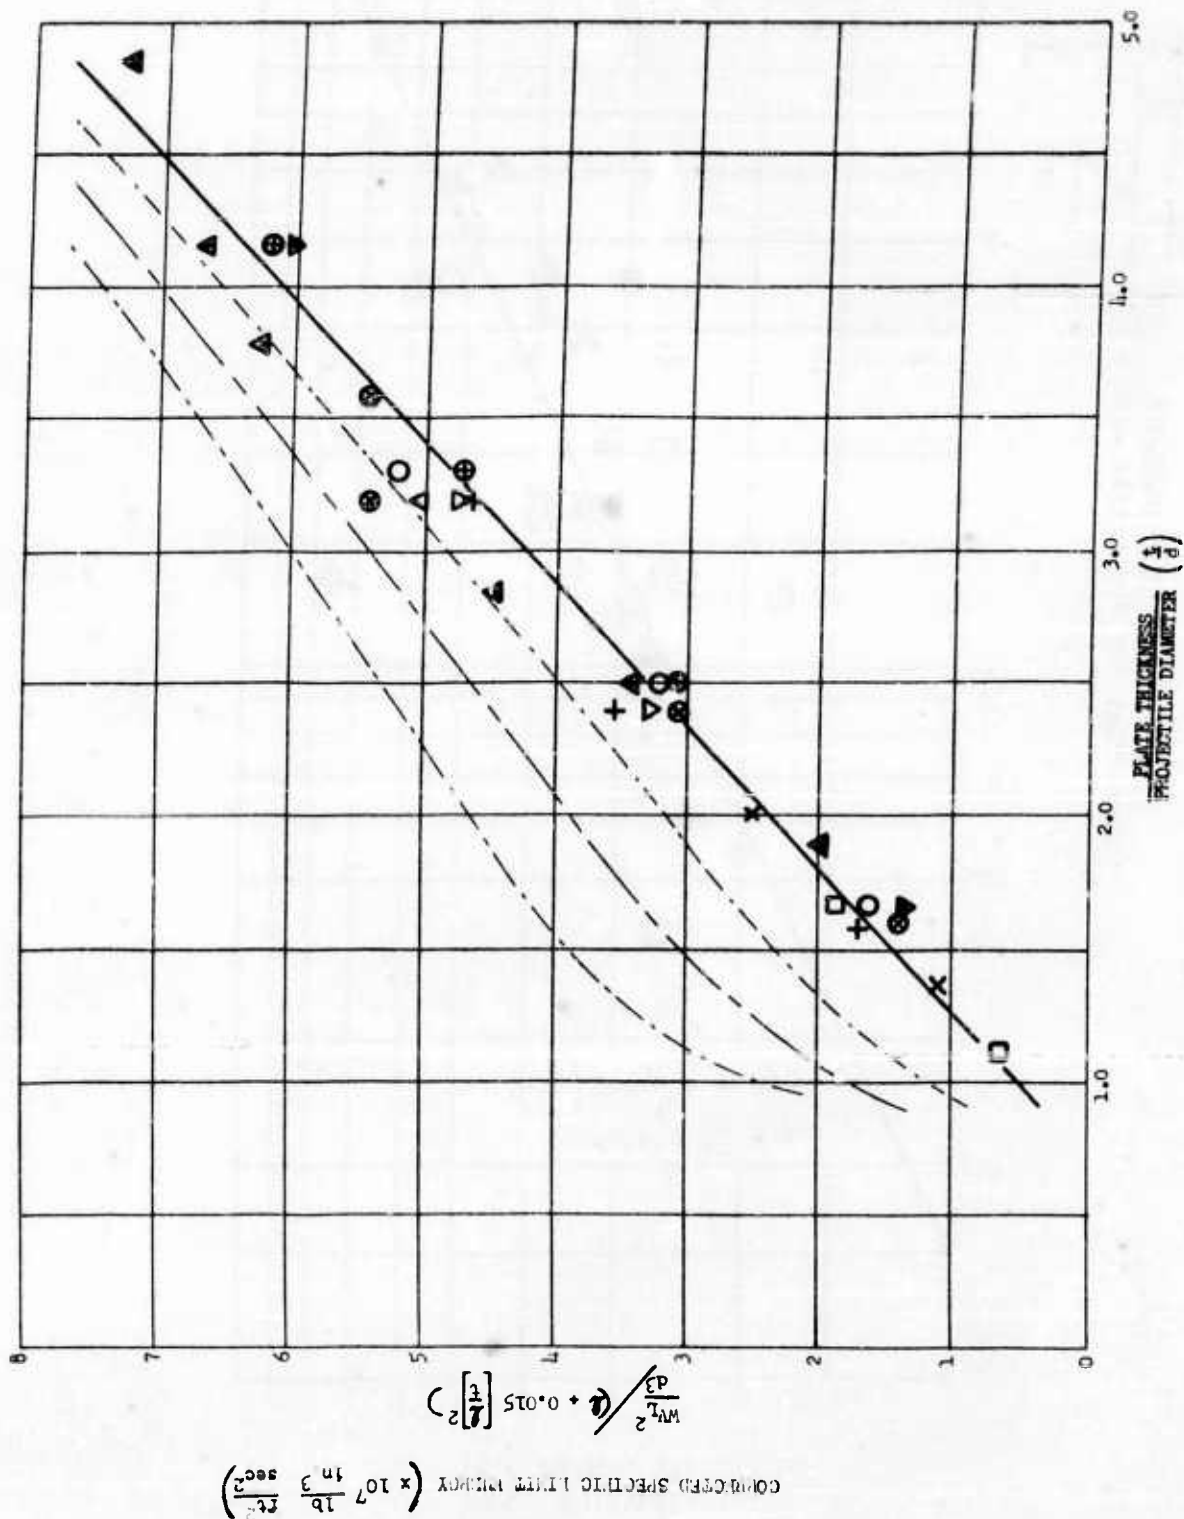


Figure 4. Perforation energy, corrected for projectile length, vs plate thickness for arrow-type monobloc steel projectiles at 60° obliquity

CONFIDENTIAL

CONFIDENTIAL

Perforation Formula for Full Caliber Projectiles

Very few perforation data are available for comparison between large and small scale solid steel arrow results at 60° obliquity. Considerably more penetration data are available for the 90/40 mm APT82 arrow projectile at 55° obliquity. These data are plotted in Figure 5, together with a few results for 60° angle of attack.

A 90/40 mm APT82 projectile, 8.57 calibers long, fired at 60° obliquity vs plate 2.6 calibers thick, had a specific limit energy of 3.3×10^7 while for the same angles of attack against plate 3.8 calibers thick, the SLE was 4.7×10^7 . Each of these values is about 20 per cent less than that predicted by the perforation formula based on the small caliber data. This is not unreasonable in view of the large difference in size.

In order to correlate the full caliber, 55° data by use of equation (1), it is to be expected that the values for some of the constants would be different than for the small caliber arrows, both because of a scale effect and a different angle of attack. As a result, the values for the constants a and b were changed to 1.4×10^7 and 0.8, respectively. Therefore,

$$SLE = 1.4 \times 10^7 \left[t/d - 0.80 \right] \left[1 + 0.015 (l/t)^2 \right]$$

It may be noted in Figure 5 that the curves plotted with this equation fall fairly close to the plotted ballistic data and, particularly, that the observed changes are in the expected directions.

CONCLUSIONS

1. For arrow-type projectiles of a given diameter, the energy required for defeating RH armor at 60° obliquity increases as the projectile length increases.
2. An equation has been developed which relates projectile length, as well as the usual projectile and plate parameters, to the energy required to defeat a target. With the adjustment of certain constants from limited firing data, the equation should be applicable to large as well as small caliber arrow-type projectiles. Also, it should reduce considerably the amount of ballistic testing.

CONFIDENTIAL

CONFIDENTIAL

36.231.35302/ORD.57
R-1436

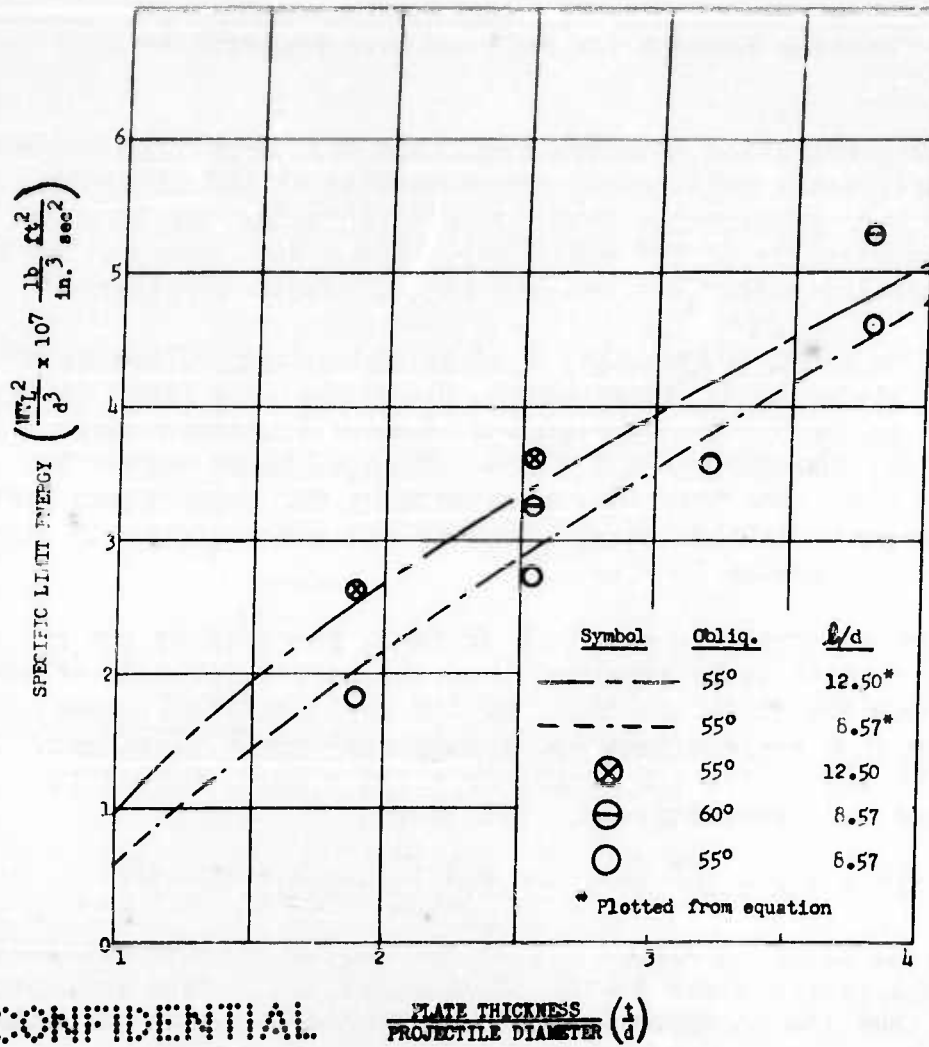


Figure 5. Perforation energy vs plate thickness for 40 mm (T82E16, E22, E23) arrow-type monobloc steel projectiles vs R4 armor at 55° and 60° obliquity

WORK IN PROGRESS

Penetration studies are being continued with Models 36, 37, 38, and 39, which have different lengths and diameters but the same weight, against a wide variety of plate thicknesses and obliquities ranging from 0° to 70°. The results of this work will be reported at a future date.

CONFIDENTIAL

CONFIDENTIAL

APPENDIX

PROJECTILE DESIGN

Penetrators

Sketches for all penetrator designs are included in Figures 6 and 7. Projectile lengths and weights are contained in Table II, which also includes weights and dimensions for launching accessories, such as carriers, stabilizers, obturators, and steel disc pushers. For ease of machining, the first projectiles (Models 14, 15, 16, 19, 33, 34, and 35 - Figure 6) had 45° included angle, conical noses. The latest four designs (Models 36 to 39 - Figure 7) had ogival noses of 1 1/2 caliber radius, similar to most conventional AP shot. There is no reason to believe that any difference in penetration performance exists between the two shapes, since all projectiles shattered at the obliquities and velocities investigated in this report.

All projectiles were machined from drill rod (1095 steel), and heat treated to Rc 62 to 65 hardness.

Stabilizers

Due to the short range (25 to 30 ft) over which the arrow projectiles were fired, they were drag-stabilized by means of disc-like aluminum alloy bases (Figure 8). Over this short range the lesser retardation afforded by fins was considered insufficient to compensate for the greater cost of machining; in addition, the range was too short for the projectile yaw to be damped out (if there is yaw) with either type of stabilizer. Penetration data obtained with projectiles having yaw (determined by means of shadowphotography and radiography) were excluded from this report.

The first base design, shown in Figure 8A, was not very successful. Shadowgraphs, which were taken of each projectile in flight, indicated that turbulence and, hence, the trailing shock wave, started far forward on the body (Figure 9). Two methods were tried to overcome this condition; the first was to attach fins (as shown in Figure 8B), the second was to taper the base (as shown in Figure 8C). Both designs showed some stability improvement; however, there was not much difference between the two. The use of fins was discontinued since they are more difficult and expensive to make.

There were indications of a tendency for the aluminum alloy base behind the arrow to plug on setback. To avoid this, a hole was drilled completely through the base and a hardened (Rc 45) steel disc was placed behind the projectile as a "pusher." This design is the one presently used in testing Models 38 and 39.

CONFIDENTIAL

36.231.S-839/ORD.58
R-1436

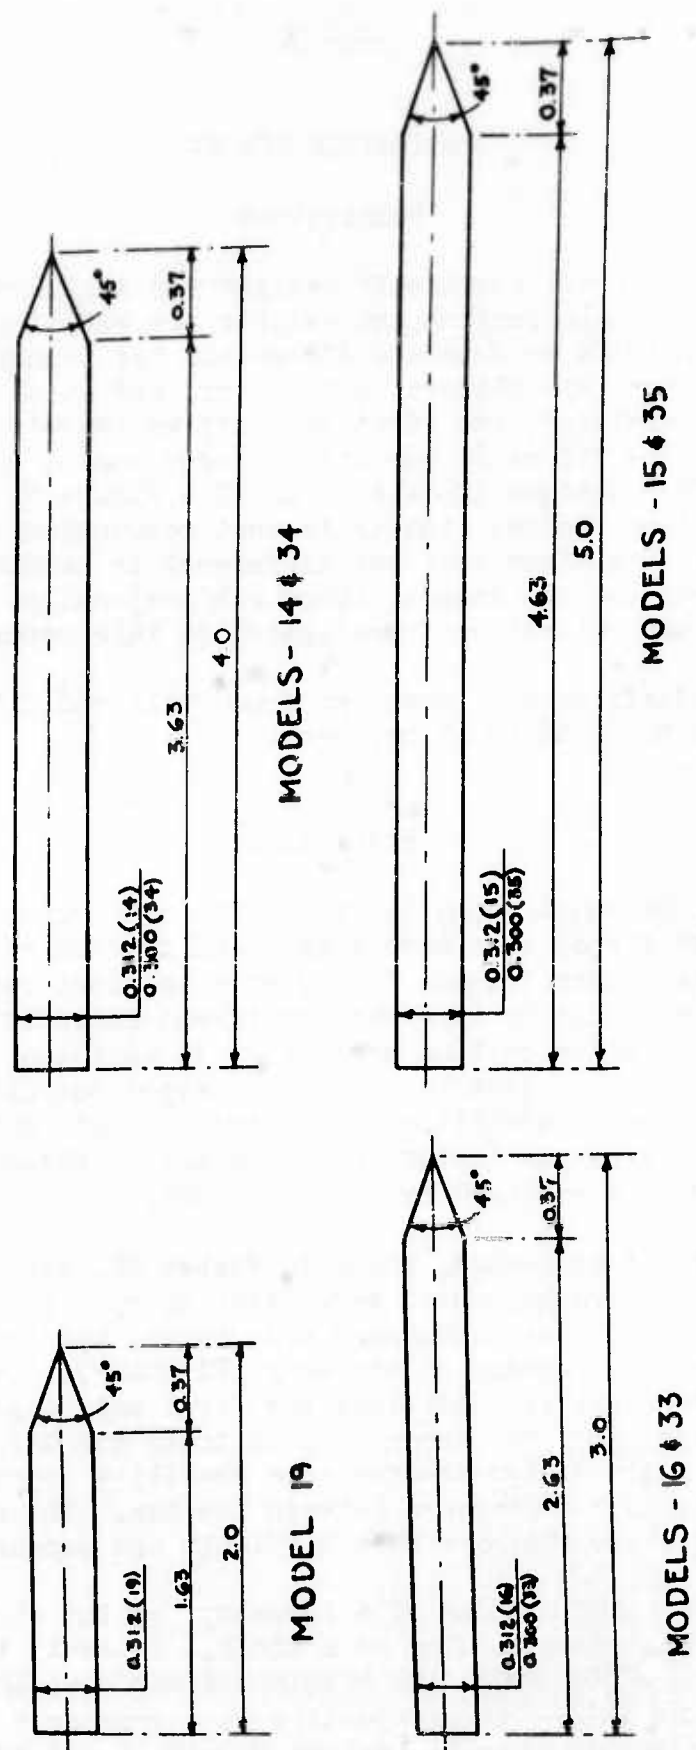


Figure 6. Penetrator designs for arrow-type projectiles

CONFIDENTIAL

CONFIDENTIAL

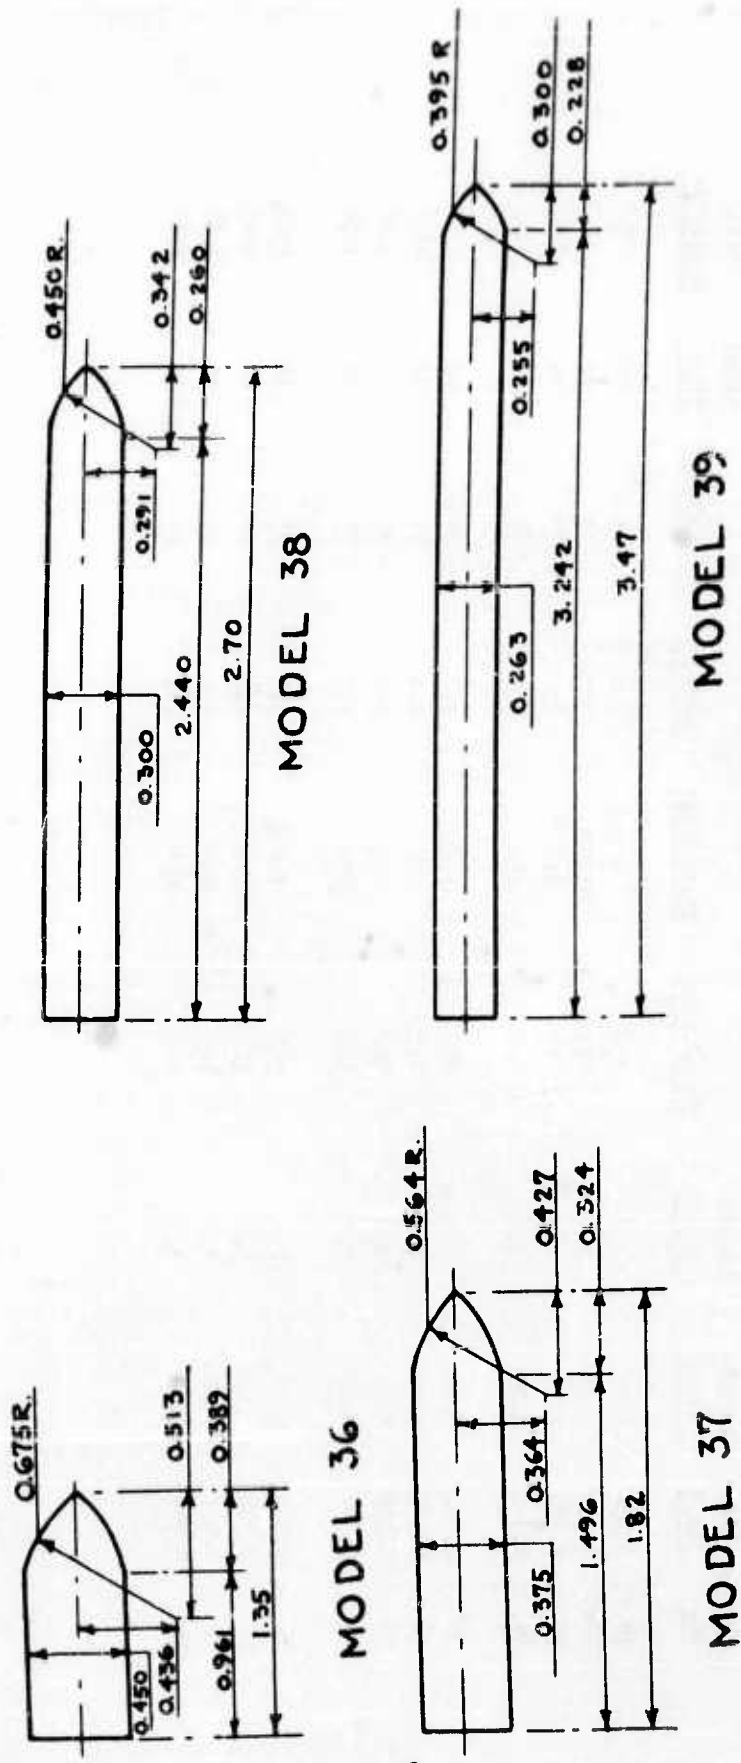


Figure 7. Penetrator designs for arrow-type projectiles

CONFIDENTIAL

CONFIDENTIAL

Table II. Projectile and Launching Accessory Characteristics

No.	Projectile		Carrier Length (in.)	Weight (gr)						Steel Disc	Total Propelled
	Dia (in.)	Length (in.)		Penetrator	Stabilizer	Carrier	Obturator				
36	0.450	1.35	1.0	355	-	220	45			130	750
37A	0.375	1.82	1.0	355	187	333	45			130	1050
37	0.375	1.82	1.0	355	211	333	79			214	1192
19	0.312	2.00	1.5	260	298	330	79			214	1181
38	0.300	2.70	2.0	355	155	421	79			214	1224
16	0.312	3.00	2.0	413	298	494	79			214	1498
39	0.300	3.00	2.0	384	171	390	79			214	1238
14	0.312	4.00	3.0	564	298	707	79			214	1852
39	0.263	3.47	2.4	355	164	517	79			214	1329
34	0.300	4.00	3.0	522	171	600	79			214	1586
15	0.312	5.00	3.0	715	298	930	79			214	2296
35	0.301	5.00	3.0	657	171	600	79			214	1721

CONFIDENTIAL

CONFIDENTIAL

36.231.35236/ORD.57
R-1436

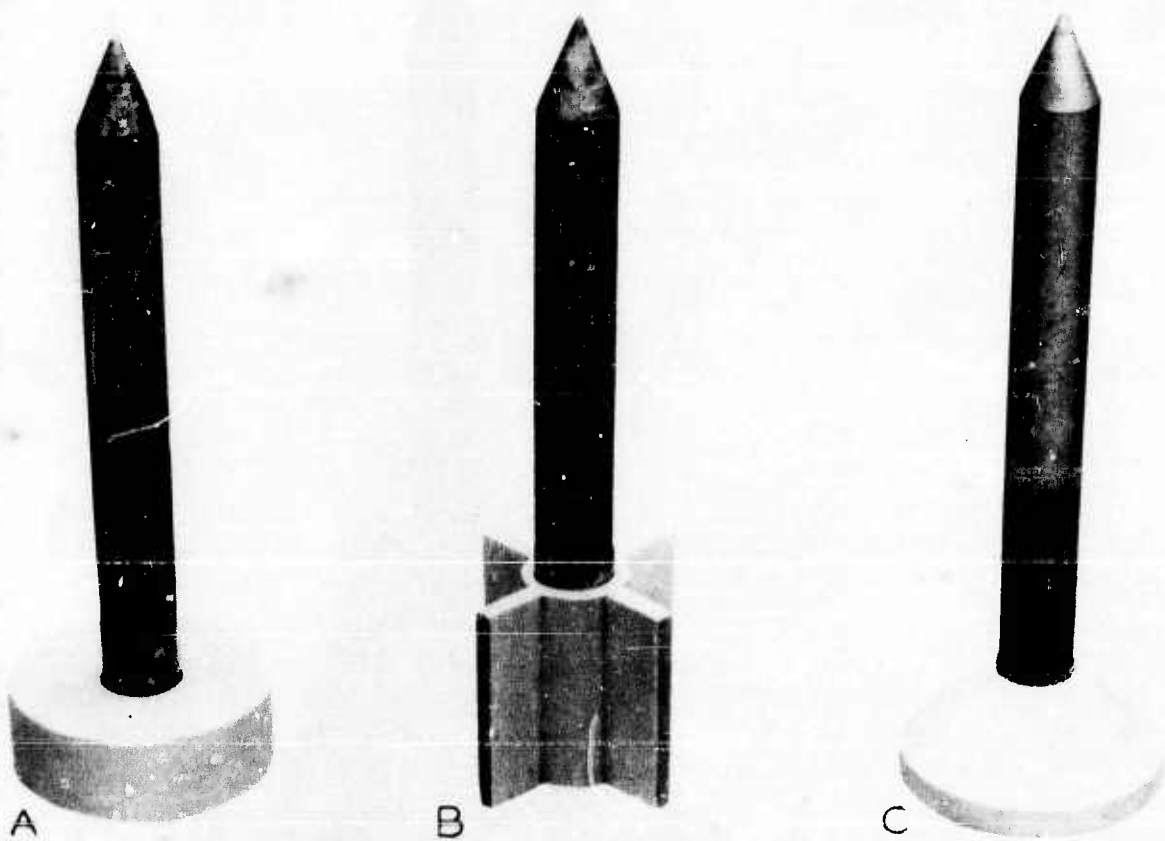


Figure 8. Stabilizer (aluminum alloy) designs for arrow-type projectiles

CONFIDENTIAL

CONFIDENTIAL

36.231.35573/ORD.57
R-1436

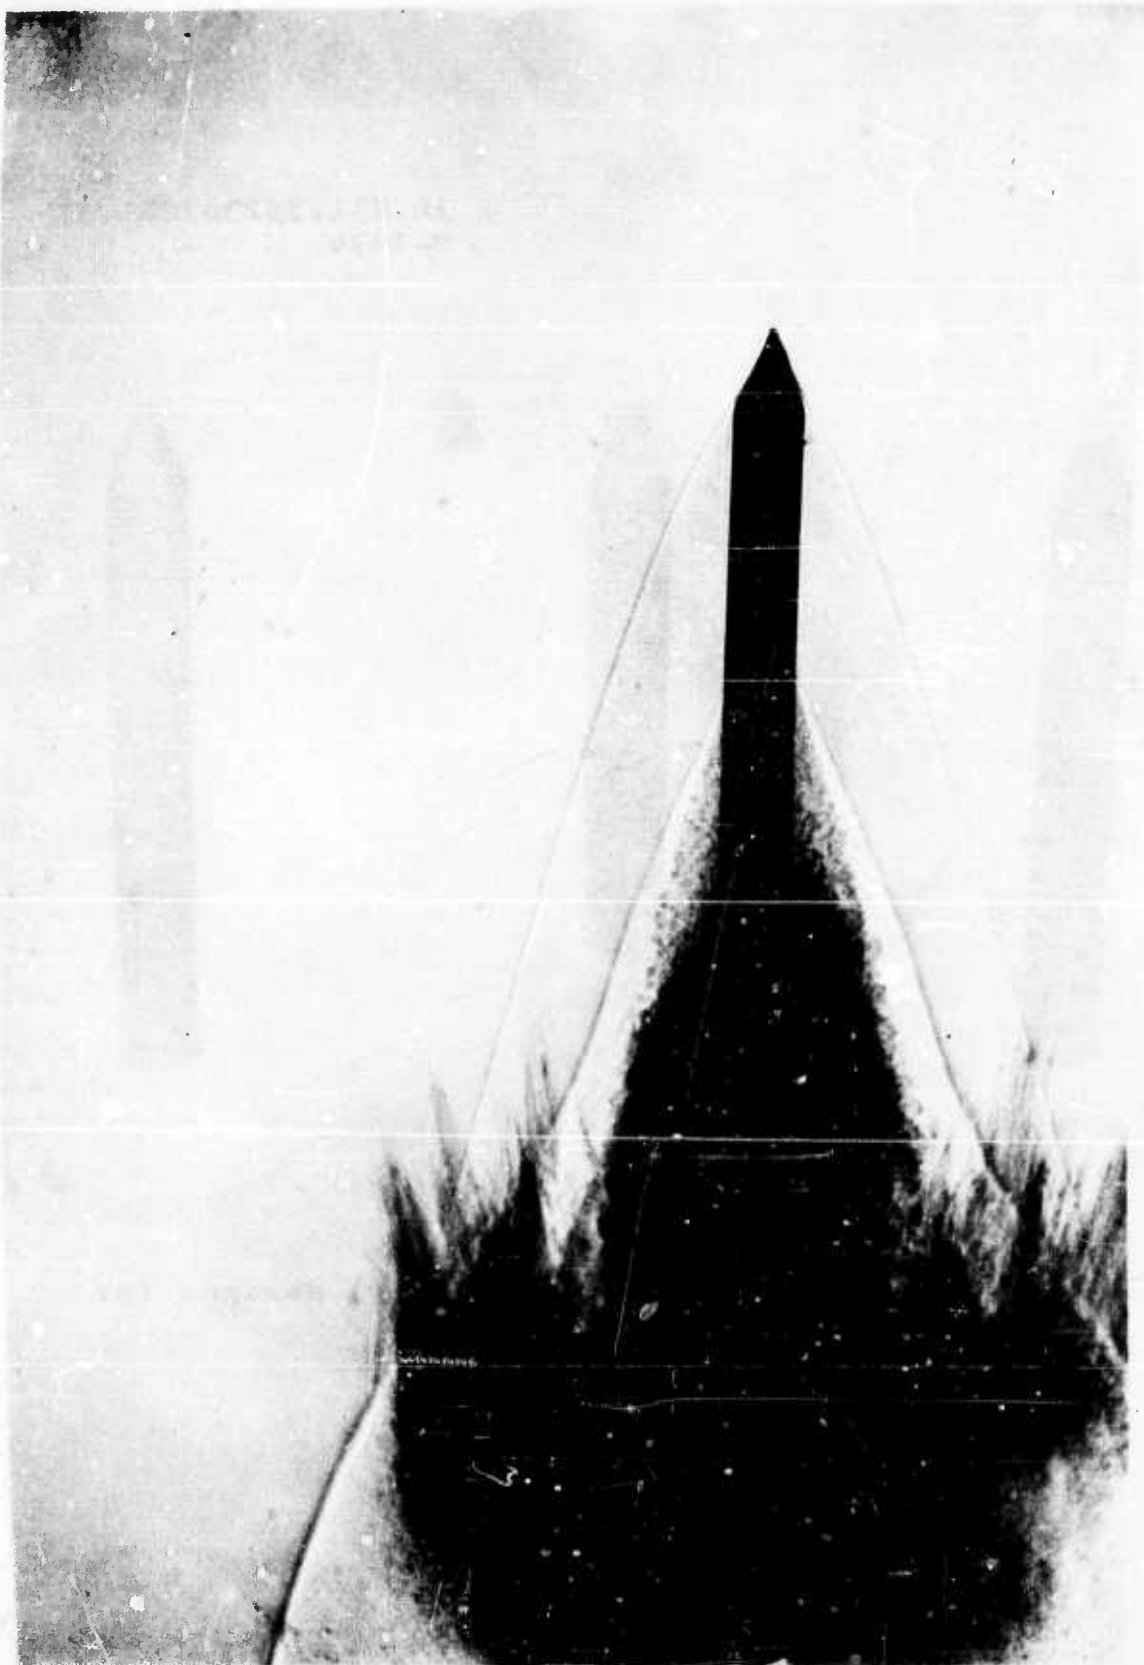


Figure 9. Shadowgraph of model 14 projectile fired at 4900 fps,
showing turbulence

CONFIDENTIAL

CONFIDENTIAL

Since drag stabilization of short projectiles ($l/d \leq 5$) was not accomplished, they were fired from a 20 mm rifled gun. Model 37 projectiles with $l/d = 4.9$ could not be stabilized by either spinning or dragging, so the possibility of combining the two types of stabilization was investigated. The first base design for this projectile, similar to the aluminum alloy design in Figure 8A, was made of steel. Since the weight of the base of this design was more than that of the penetrator, the modification (similar to Figure 8C), as shown in Figure 10, was made and is now in use for Model 37 projectiles.

Sabots

In firing Models 36 and 37 from rifled guns, two types of plastic (A and B)* were tried. Plastic A did not have sufficient strength; therefore two designs (Figure 11) of Plastic B were tried. Design 1 could possibly have been used for low velocity firing of Model 36 projectiles, but the plastic broke in the gun at higher velocities and pressures; design 2 was therefore adopted. Model 37 projectiles fired with design 1 sabots were not stable due to launching and exterior ballistic deficiencies; therefore design 2 was used for this model.

For all models fired from a smooth bore gun, Plastic A has proven adequate. The first design used is shown in Figure 12A. The longitudinal slots were machined to assist the sabots in discarding. The later sabots (Figure 12B) were made of four segments for ease in machining and facility in discarding.

Neoprene discs, 1/4 inch thick, were used as obturators behind all projectiles.

LAUNCHING DEVICES

Guns

Projectiles, Models 36 and 37, were fired from 20 mm, standard twist, rifled guns. The barrel travel length varied from 52 to 138 inches; one Mann-type barrel or two joined together were used to obtain the desired velocities. The barrel at the breech end was machined to permit insertion of the round, but was not chambered.

*See Code Sheet

CONFIDENTIAL

36.231.35237/ORD.57
R-1436



Figure 10. Stabilizer (steel) design for arrow-type projectile
(Model 37)

CONFIDENTIAL

CONFIDENTIAL

36.231.35307/ORD.57
R-1436

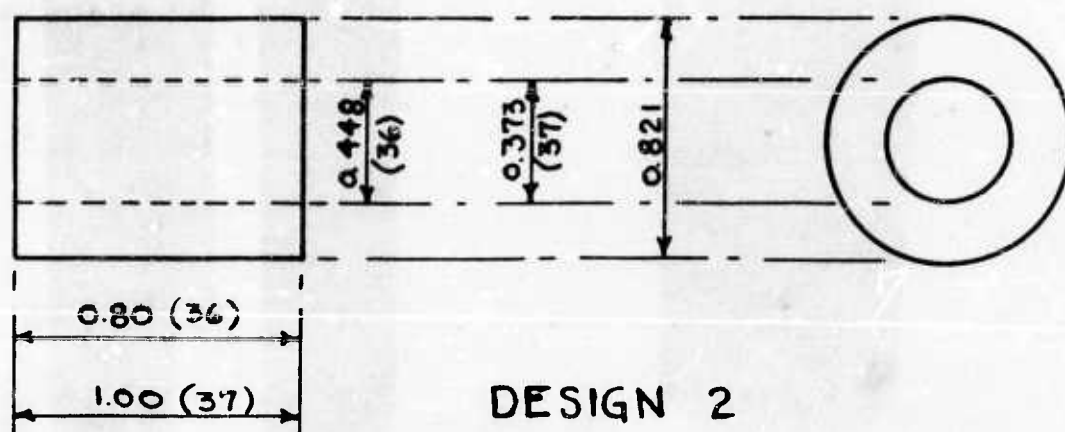
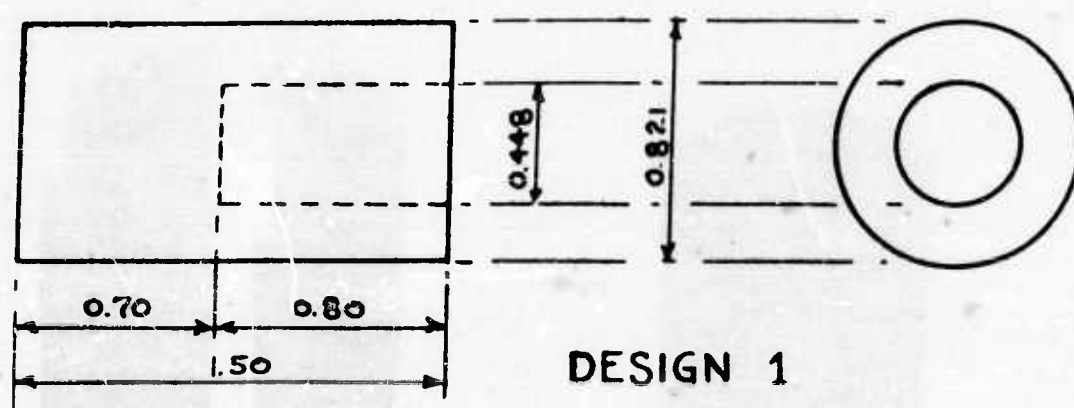


Figure 11. Sabot designs (plastic) for arrow-type projectiles

CONFIDENTIAL

36.231.35235/ORD.57
R-1436

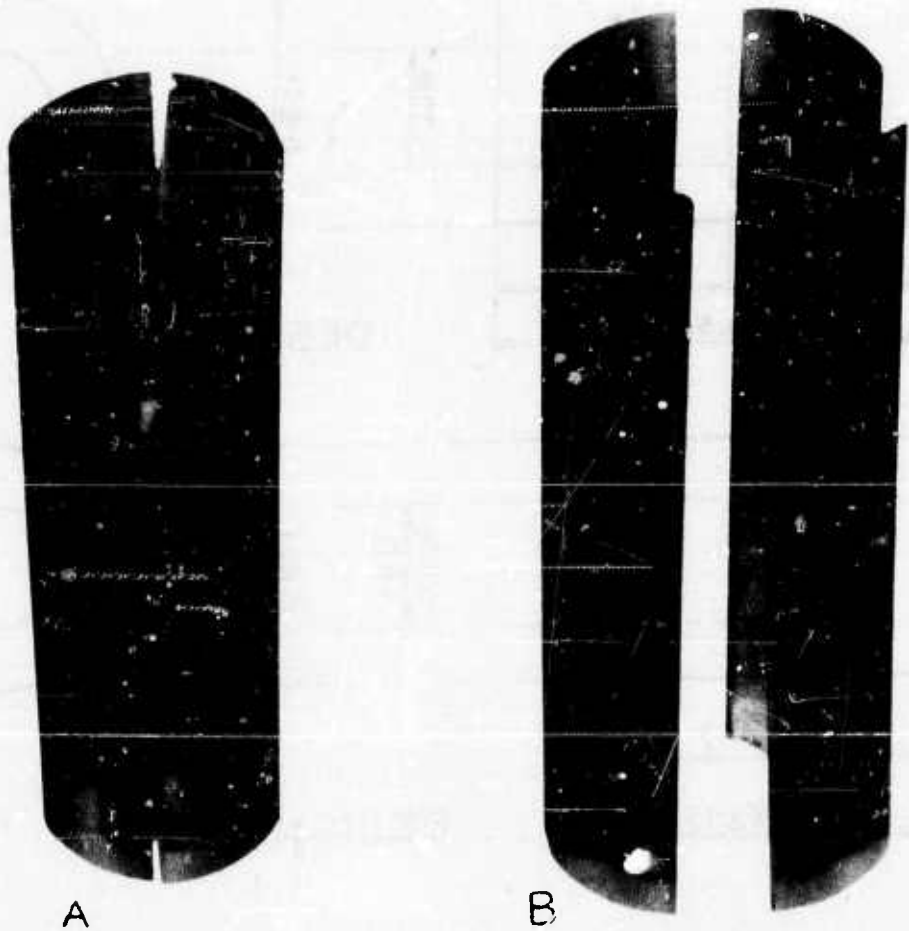


Figure 12. Sabot designs (plastic) for arrow-type projectiles

CONFIDENTIAL

CONFIDENTIAL

All other projectiles were fired from 27 mm blank (unrifled) barrels. The travel length in these tubes ranged from 60 to 154 inches. Either single or double length Mann-type barrels were used. In addition, one of the double length barrels was adapted for vacuum firing. A barrel pressure of less than one millimeter of mercury was achieved prior to firing.

Chambers

Depending upon the velocity desired, one of three chambers was used. For relatively low velocities (1800 to 3600 fps), an un-necked caliber .60 cartridge case was used in a modified conventional size chamber.

For higher velocities (3200 to 5500 fps), the chamber shown in Figure 13 was used. This chamber has two pressure stations which permit the taking of simultaneous pressure measurements. With this chamber, no cartridge case was used with the exception of a one-inch base section cut from a caliber .60 case. The base section was used to hold the primer and perforated flash tube. With only a primer, a large pressure differential was observed between the front and rear pressure stations. To equalize these pressures, different methods were tried, including front ignition, central ignition, empty perforated flash tubes, and flash tubes partially filled with black powder. The empty perforated flash tube gave the best results. If a combination of powders was required, it was found that the placing of the slower powder near the primer and the faster powder near the projectile was more satisfactory than blending the powders.

For hyper velocities (4400 to 7000 fps), the chamber shown in Figure 14 was used. A one-inch section of a caliber .60 cartridge case was used, similar to the one used for the chamber of Figure 13. Although the projectile velocities obtained with this chamber overlap those obtained with the previous one, the pressures are much lower for similar velocities. The flash tube system proved to be unnecessary for this chamber. However, it was found that FFG black powder adjacent to the primer was needed for proper ignition.

In all cases M52A4 electric primers were used.

Inasmuch as none of the projectiles were crimped into the case, it was found that more consistent ignition and more reproducible velocities could be obtained by placing a thin brass disc between the chamber and the gun tube.

Copper crusher gages were used for all rounds, except for a few where piezoelectric gages were used.

36.231.35309/ORD.57
R-1436

CONFIDENTIAL

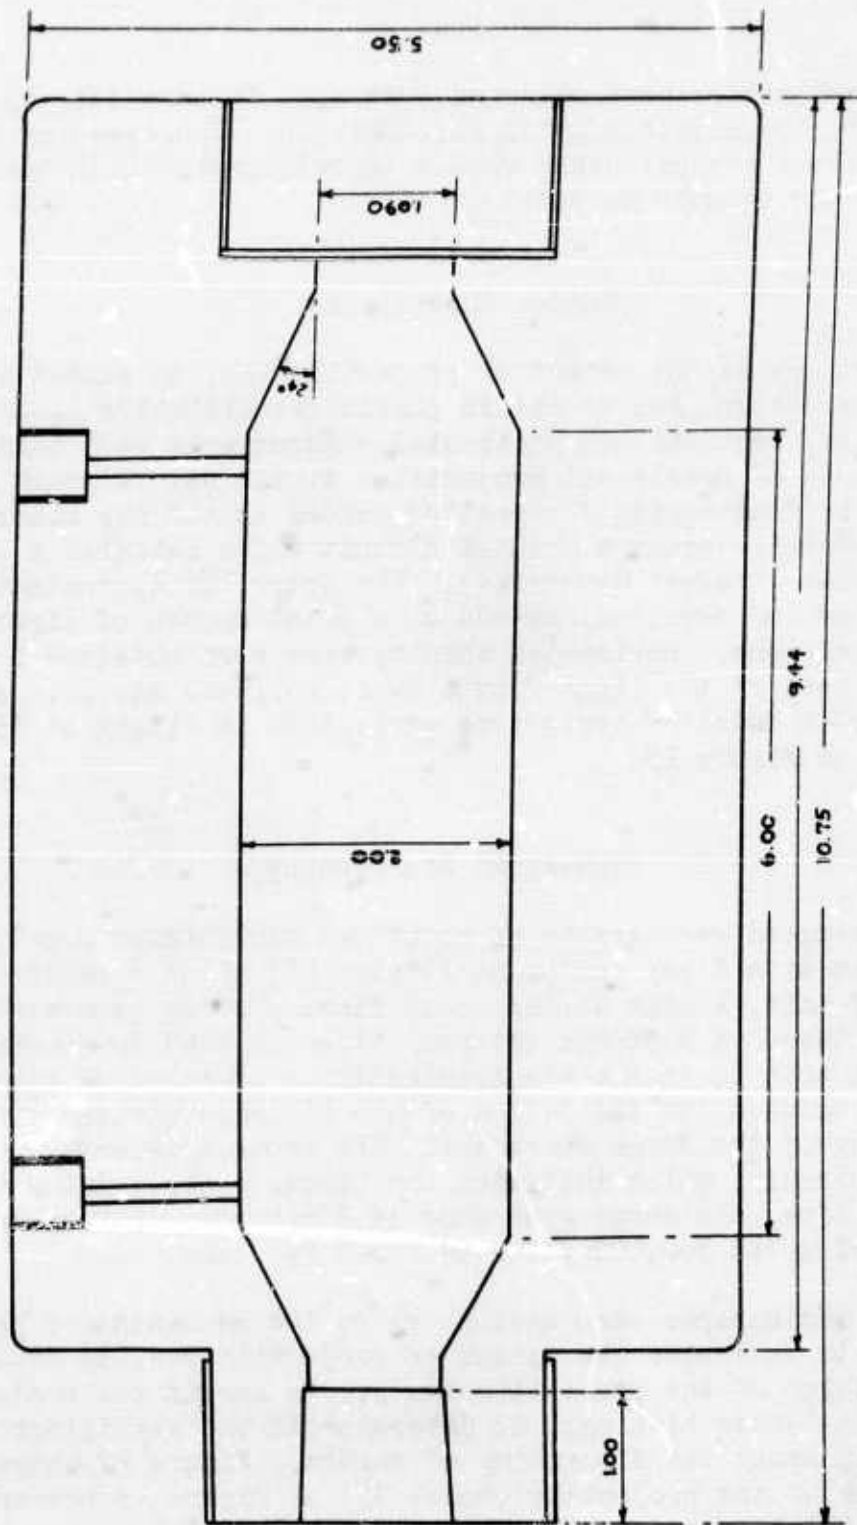


Figure 14. Sketch of chamber for arrow-type projectile velocities of 4400 to 7000 fps

CONFIDENTIAL

CONFIDENTIAL

INSTRUMENTATION

Velocity

All velocities were measured over a 10-ft base line by means of 1- or 1.6-megacycle counter chronographs. The breaking of a printed silver circuit discharged a thyratron which, in turn, initiated the counter to start or stop.

Shadow Photography

To determine the extent of projectile yaw, to assist in projectile design, and to obtain possible qualitative aerodynamic information, vertical and horizontal shadowgraphs were taken simultaneously of nearly all projectiles in flight. A spark was obtained by discharging a capacitor across an air gap after the fired projectile broke a printed circuit which actuated a delay unit (Preset Interval Generator). The spark, of approximately one microsecond duration, served as a point source of light for the shadowgraphs. Horizontal shadowgraphs were obtained by reflecting part of the light from a front surfaced mirror. An example of a Model 39 arrow-type projectile in flight at 5565 fps is shown in Figure 15.

High-speed Radiography

High-speed radiographs of about one microsecond duration were taken with X-ray equipment (Figure 16) which consists of a control unit, a high voltage rectifier, a surge generator, and an X-ray tube. A micronex interval timer is used in conjunction with this unit to insert electronically, a preselected time interval between the initiation of the timing cycle and the triggering of the surge generator. The projectile breaks a printed circuit, which initiates the timing cycle. After the selected time, the surge generator is discharged, giving an impulse of up to 360,000 volts to the X-ray tube.


The radiographs were used to study the mechanism of penetration, to determine the extent of projectile yaw, to determine the condition of the projectile (e. g., to see if the projectile was intact before hitting), to determine if the stabilizer was on, and to study the discarding of sabots. Figure 17 shows a radiograph of the projectile (Model 35) of Figure 15 penetrating 1/2 inch thick armor at 60° obliquity, at 3185 fps.

CONFIDENTIAL

36.231.S-841/ORD.58
R-1436



A

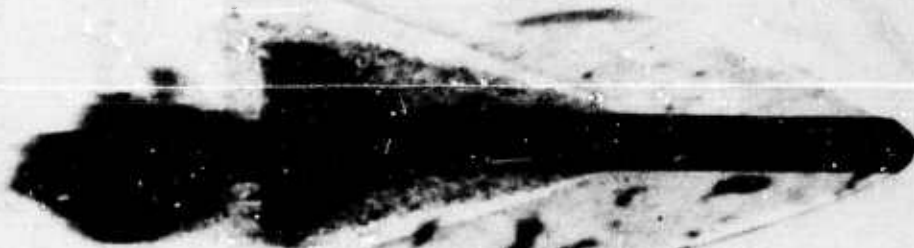

B

Figure 15. Shadowgraphs of arrow-type projectile (Model 39)
at 5565 fps

A - In vertical plane
B - In horizontal plane

CONFIDENTIAL

36.231.S-842/ORD.58
R-1436

CONFIDENTIAL

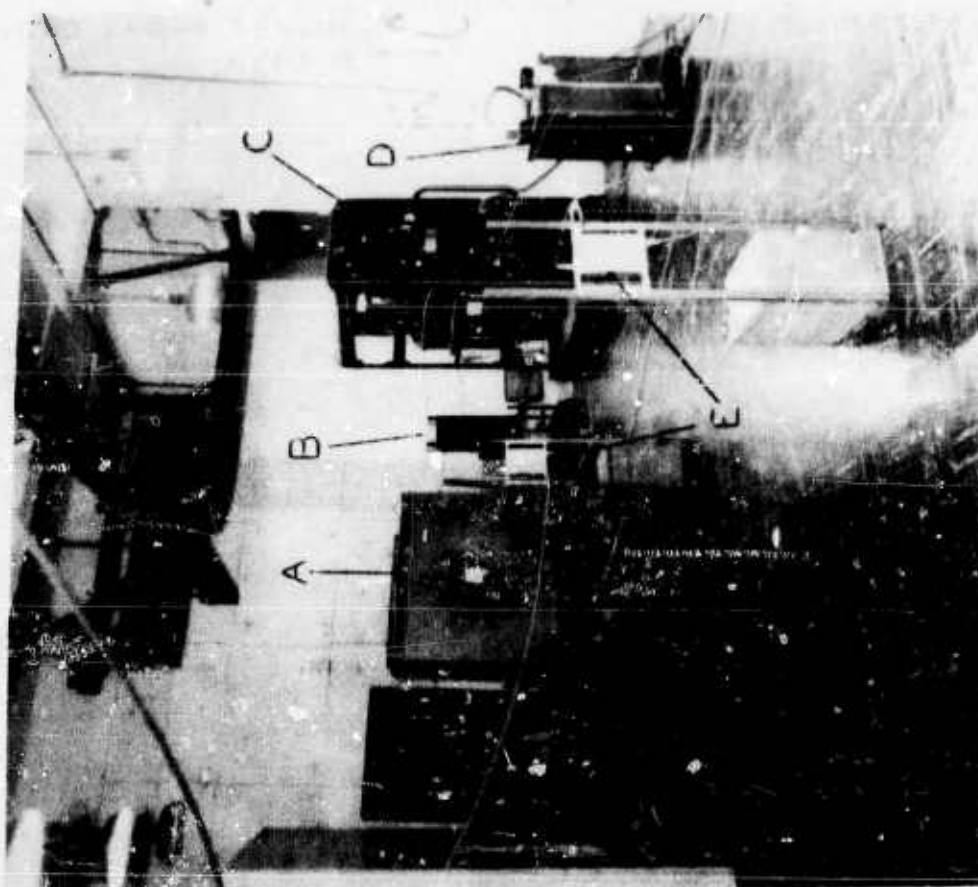


Figure 16B. X-ray range setup

- A - Fragment protection box
- B - X-ray tube (in oil)
- C - Surge generator
- D - Rectifier unit
- E - Velocity screens

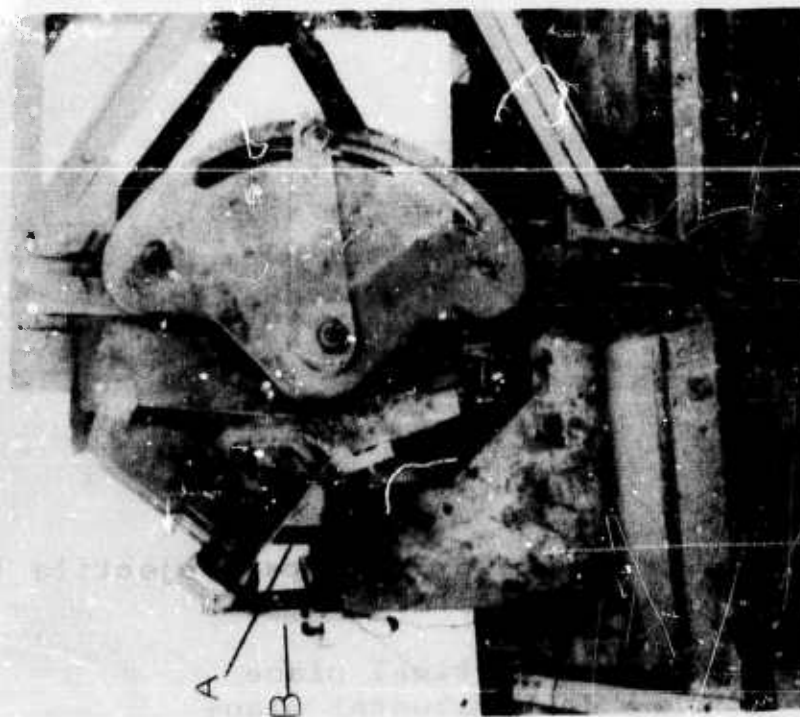


Figure 16A. Plate mount with fragment protection box removed

- A - Cassette
- B - X-ray triggering screen
- C - Plate

CONFIDENTIAL

36.231.35576/ORD.57
R-1436

CONFIDENTIAL



35 2.3

Figure 17. Radiograph of arrow-type projectile (Model 35) penetrating 1/2 inch RH armor at 60° obliquity, at 3185 fps

CONFIDENTIAL²⁷

CONFIDENTIAL

DISTRIBUTION

- 1 - Chief of Ordnance
Department Army
Washington 25, D. C.
Attn: ORDTA
- 1 - Attn: ORDTB
- 1 - Attn: ORDIM
- 1 - Commanding General
Ordnance Ammunition Command
U. S. Army
Joliet, Illinois
Attn: Materials Eng
- 1 - Commanding Officer
Springfield Armory
Springfield 1, Mass.
Attn: Eng Dept
- 1 - Commanding General
Picatinny Arsenal
Dover, New Jersey
Attn: Tech Group
- 1 - Attn: J. E. Rainier, SFAL
- 1 - Commanding Officer
Rock Island Arsenal
Rock Island, Illinois
Attn: Laboratory
- 1 - Commanding Officer
Watertown Arsenal
Watertown 72, Mass.
Attn: Tech Group
- 1 - Attn: E. Abbott, WAL
- 1 - Director
Ordnance Materials Research Office
Watertown Arsenal
Watertown 72, Mass.
- 2 - Commander
Ordnance Weapons Command
Rock Island Arsenal
Rock Island, Illinois
Attn: ORDOW-TX
- 1 - Commanding General
Aberdeen Proving Ground
Maryland
Attn: Lab Serv Div
- 1 - Attn: D&PS, Ammunition Br
- 1 - Attn: D&PS, Armor Br
- 1 - Attn: Ball Res Lab
- 1 - Attn: Tech Info Br, Bldg 313
- 1 - Commanding Officer
Lake City Arsenal
Independence, Missouri
Attn: Dr. Shratter
- 1 - Commander
Army Ballistics Missile Agency
Redstone Arsenal
Huntsville, Alabama
- 1 - Commander
Ordnance-Tank Automotive Command
Detroit Arsenal
Center Line, Michigan
Attn: R & D Div
- 1 - Commanding Officer
Diamond Ordnance Fuze Labs
Washington 25, D. C.
Attn: Tech Inf. Sect
ORDTL 06.33
- 5 - Armed Services Technical
Information Agency
Document Service Center
Arlington Hall Station
Arlington 12, Va.
Attn: DSC-SD (Code 3)

CONFIDENTIAL

CONFIDENTIAL

- 1 - Chief
Bureau of Ordnance
Navy Department
Washington 25, D. C.
- 1 - Chief
Bureau of Aeronautics
Navy Department
Washington 25, D. C.
- 1 - Chief
Bureau of Ships
Navy Department
Washington 25, D. C.
Attn: Code 342
- 1 - Director
Naval Research Laboratories
Washington 25, D. C.
- 1 - Commander
Naval Ordnance Laboratories
Silver Spring 19, Maryland
- 1 - Commandant
U. S. Naval Proving Ground
Dahlgren, Virginia
Attn: Terminal Ballistics Lab
- 1 - Commanding General
Wright Air Development Center
Wright-Patterson Air Force Base
Dayton, Ohio
- 1 - Headquarters
Air Research and Development Command
P. O. Box 1395
Baltimore 3, Maryland
Attn: RDTDPA

CONFIDENTIAL

UNCLASSIFIED

UNCLASSIFIED