

UNCLASSIFIED

AD 266 386

*Reproduced
by the*

ARMED SERVICES TECHNICAL INFORMATION AGENCY
ARLINGTON HALL STATION
ARLINGTON 12, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

AD



10

WAL TR 830.3/7

266386

WATERTOWN ARSENAL LABORATORIES

THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS ON THE RECRYSTALLIZATION OF NICKEL

TECHNICAL REPORT NO. WAL TR 830.3/7

XON

BY

ERNEST P. ABRAHAMSON, II

DATE OF ISSUE - NOVEMBER 1961

ACCEPTED
 NOV 15 1961
 WATERTOWN ARSENAL
 TR DR

OMS CODE 5010.11.8050051
 GENERAL MATERIALS PROBLEMS, RESEARCH AND INVESTIGATION
 D/A PROJECT 5893-32-001

WATERTOWN ARSENAL
 WATERTOWN 72, MASS.

AD 100-
 FILE COPY

AD

Recrystallization
Transition elements
Nickel

THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS
ON THE RECRYSTALLIZATION OF NICKEL

Technical Report No. WAL TR 830.3/7

By

Ernest P. Abrahamson, II

Date of Issue - November 1961

OMS Code 5010.11.8050051
General Materials Problems, Research and Investigation
D/A Project 5B93-32-001

WATERTOWN ARSENAL
WATERTOWN 72, MASS.


WATERTOWN ARSENAL LABORATORIES

TITLE


THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS
ON THE RECRYSTALLIZATION OF NICKEL

ABSTRACT

The effect of transition element binary solid solution additions upon the recrystallization temperature of nickel has been investigated. All additions raised the recrystallization temperature. Both the rate of change of recrystallization temperature with atomic percent solute and the limit of initial linearity are found to correlate with the free atom ground state outer electron configuration of the solute element.


ERNEST P. ABRAHAMSON, II
Supervisory Physical Metallurgist

APPROVED:


J. F. SULLIVAN
Director
Watertown Arsenal Laboratories

INTRODUCTION

The work of Abrahamson, et al,¹⁻⁷ on dilute binary solid solution alloys indicated a correlation between the free atom ground state electron configuration of the solute and both the brittle-ductile transition and recrystallization temperature. Further, it has been shown^{3,4} that the limit of initial linearity may also be correlated with the solute electron configuration. Since previous studies have dealt with body-centered-cubic and hexagonal-close-packed solvents, this study was made to note what effect, if any, the face-centered-cubic base structure might have.

Olsen⁸ has studied the effect of some trace elements upon the recrystallization of nickel. He included only Ti, Zr, W, Mn and Co of the transition elements. The differences in change of recrystallization temperature were attributed to the solute atom size and its solubility in nickel.

PROCEDURE

All alloys were made using 99.9+ percent nickel with 0.003 C, 0.015 Fe, 0.007 O, and 0.0007 H. The solute elements were 99.9+ percent pure. According to the published binary phase diagrams⁹ and metallographic examinations at 750X, all alloys used were in solid solution.

The alloys were arc melted and remelted four times in the form of cubic 200-gram buttons under an argon atmosphere. They were then hot forged at 800 C to 0.750-inch diameter, machined to 0.60-inch, vacuum annealed for one hour at 700 C, swaged to 0.40-inch diameter, and annealed at 700 C for one hour in vacuum. The grain size was checked and found to be 77 ± 20 grains per sq mm. The specimens were then swaged to 0.187-inch diameter rod, yielding 76 ± 1 percent cold work. All alloys were then chemically analyzed for the solute addition. The interstitial contents remained the same as the values of the starting material when checked on random alloy specimens.

The swaged rod was cut into 8.25-inch lengths and heat treated in a gradient furnace for one hour. The gradient was maintained at 250 to 850 C over an 8-inch length, and recorded by 12 thermocouples. Control was ± 3 C, accomplished at the hot end.

The recrystallization was determined metallographically over the entire specimen. The criterion chosen was that point on the specimen showing the first recrystallized grain at a constant magnification, 200X. Specimens were repeated, and the agreement was found to be generally ± 3 C.

RESULTS

Seven different pure nickel specimens were tested, and the recrystallization temperature was found to be 355 ± 3 C. Figures 1 through 3 show the effect of the transition elements on the recrystallization of nickel. All elements immediately raise the recrystallization temperature.

If one considers the slope of the curves in Figures 1 through 3, a definite periodicity can be noted. Further, the limit of initial linearity is also periodic. A plot of these two parameters versus the free atom ground state outer d shell electron configuration¹⁰ demonstrates this periodicity, c.f. Figures 4 and 5.

DISCUSSION

As in previous systematic studies,¹⁻⁷ a correlation is noted between the change in recrystallization temperature with solute, and the number of outer d shell electrons in the solute. All of the curves studied have been in the form of upright or inverse V's with the apex of the $s = 2$ electron curve consistently occurring at one d electron more than the solvent.

On this basis, nickel would be expected to have an apex in the $s = 2$ curve at d^9 . Unfortunately there are no elements which exist with configurations of $d^9 s^2$ or $d^{10} s^2$ to check this. However, the positioning of the $s = 0$ curve strongly suggests that the apex occurs at d^9 .

When one considers the difference in recrystallization parameter and purity of the base metal used by Olsen, the comparison of ΔT 's is quite good. In general the data of Olsen is somewhat higher than that of this study, but the relative trend of the slope values is in agreement with the correlation. In considering Olsen's suggestion that the differences in recrystallization temperature can be attributed to the solute atom size and its solubility, a careful check of all of the systems studied, c.f. table, does not show any direct relationship.

It is felt that both atomic size and solubility limit can be considered to be functions of electronic make-up and the interaction of electron band structures in alloys. Thus rough correlation with these parameters would be expected. However, it appears that direct correlation with the electronic structure of the individual atoms yields more consistent results.

The correlation curve for the limit of linearity versus the number of solute outer d shell electrons is implied to be in the form of an inverse V, with an apex at d^9 . This assumption is based on the same reasoning as for the slope correlation curve.

These results tend to suggest that the solvent lattice structure does not effect the electron configuration correlation. There yet remains the

combination of results from the results on body-centered-cubic, hexagonal-close-packed, and the face-centered-cubic solvent material to attempt to yield a workable theory and set of equations. This will be considered in detail in a later report.

SUMMARY DATA FOR NICKEL ALLOY SYSTEMS

System	Solute Goldschmidt Atomic Radius	Percent Deviation From Solvent	Room Temp Solubility Limit at. %	Initial Slope deg C/at. %	Limit of Linearity at. %
Ni	1.25	-	-	-	-
Ni-Ti	1.47	+17.6	~ 5	+2200	.074
Ni-V	1.36	+8.8	~ 13	*	*
Ni-Mn	1.12	-10.4	37	+640	.178
Ni-Cr	1.28	+2.4	32	+1400	.068
Ni-Fe	1.28	+2.4	~ 20	+300	.255
Ni-Co	1.25	0.0	~ 60	+180	.285
Ni-Zr	1.60	+28.0	>.3	+5500	*
Ni-Cb	1.47	+17.6	~ 5	+2000	.054
Ni-Mo	1.40	+12.0	~ 10	+1150	.072
Ni-Ru	1.34	+7.2	>12	+510	.145
Ni-Rb	1.34	+7.2	**	+250	.180
Ni-Pd	1.37	+9.6	100	+700	.050
Ni-Hf	1.59	+27.2	**	+3050	*
Ni-Ta	1.47	+17.6	~ 2	+1650	*
Ni-W	1.41	+12.8	12	+960	*
Ni-Re	1.38	+8.8	**	+500	*
Ni-Os	1.35	+8.0	5	+280	.226
Ni-Ir	1.35	+8.0	**	+340	.105
Ni-Pt	1.38	+10.4	20	+170	*

* No Test Data

** Unknown


CONCLUSION

1. All transition elements studied raised the recrystallization temperature of nickel.


2. A correlation is noted between the slope of the recrystallization temperature versus atomic percent solute curve and the limit of linearity and the number of outer d shell electrons attributed to the solute atom in the ground state. The curve is in the form of a V with an apex at d^9 .

ACKNOWLEDGMENTS


The author wishes to thank the Watertown Arsenal Metallurgical Services, Analytical Chemistry and Fundamental Research Branches for their assistance. He further wishes to thank Mr. D. Tracy for his assistance and Mr. J. A. Alexander and Dr. F. Rhines for their helpful discussions.

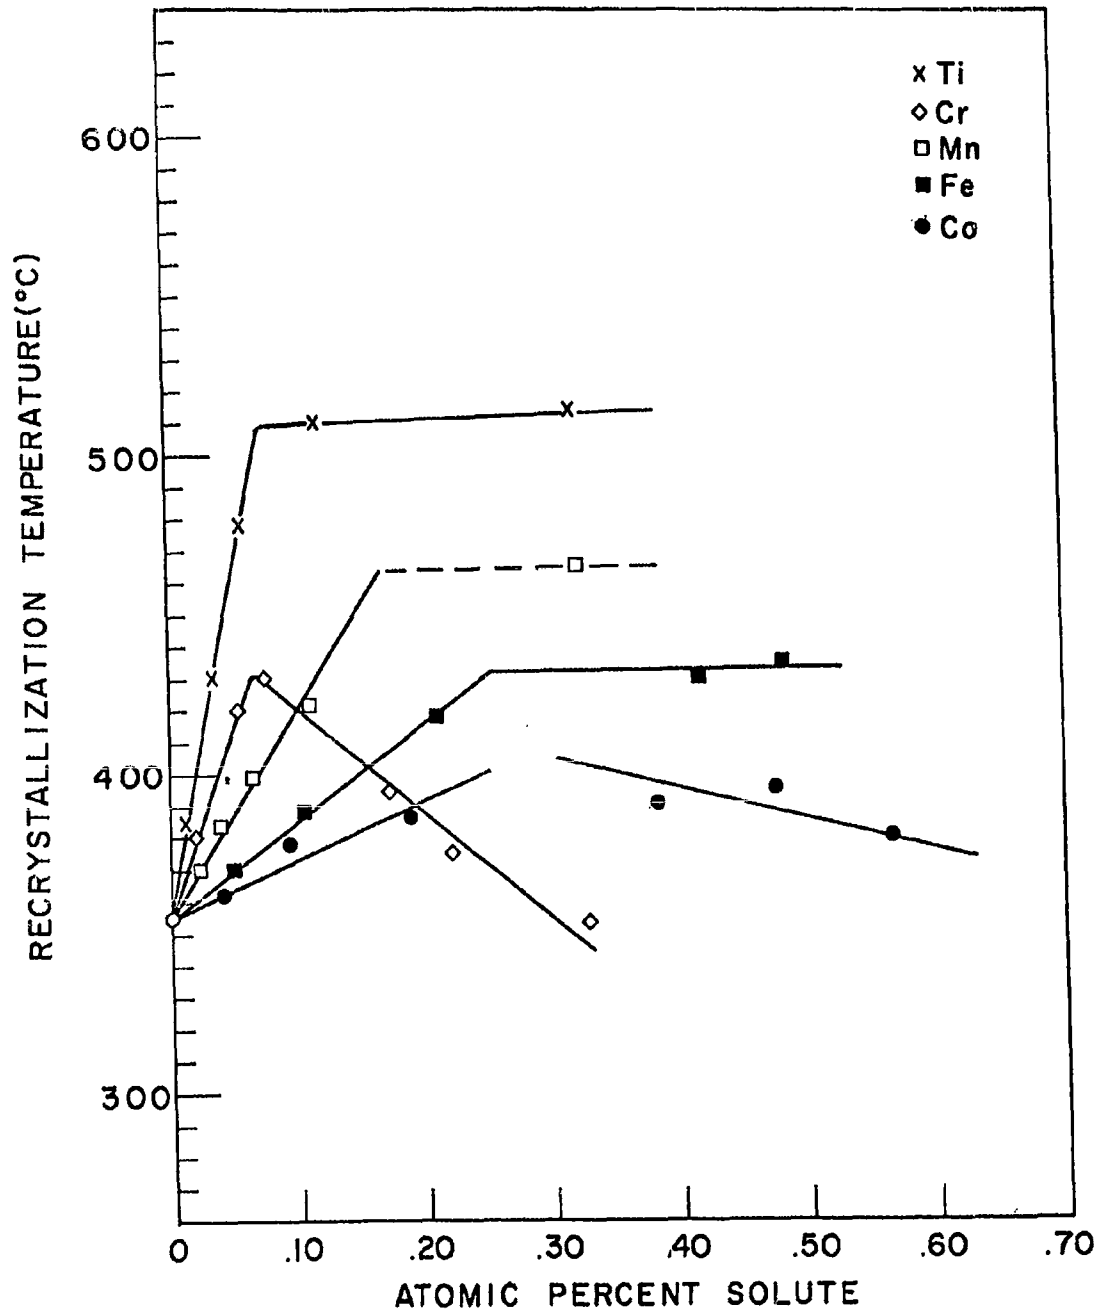


RECRYSTALLIZATION TEMPERATURE VERSUS ATOMIC PERCENT SOLUTE FOR THE FIRST TRANSITION SERIES.

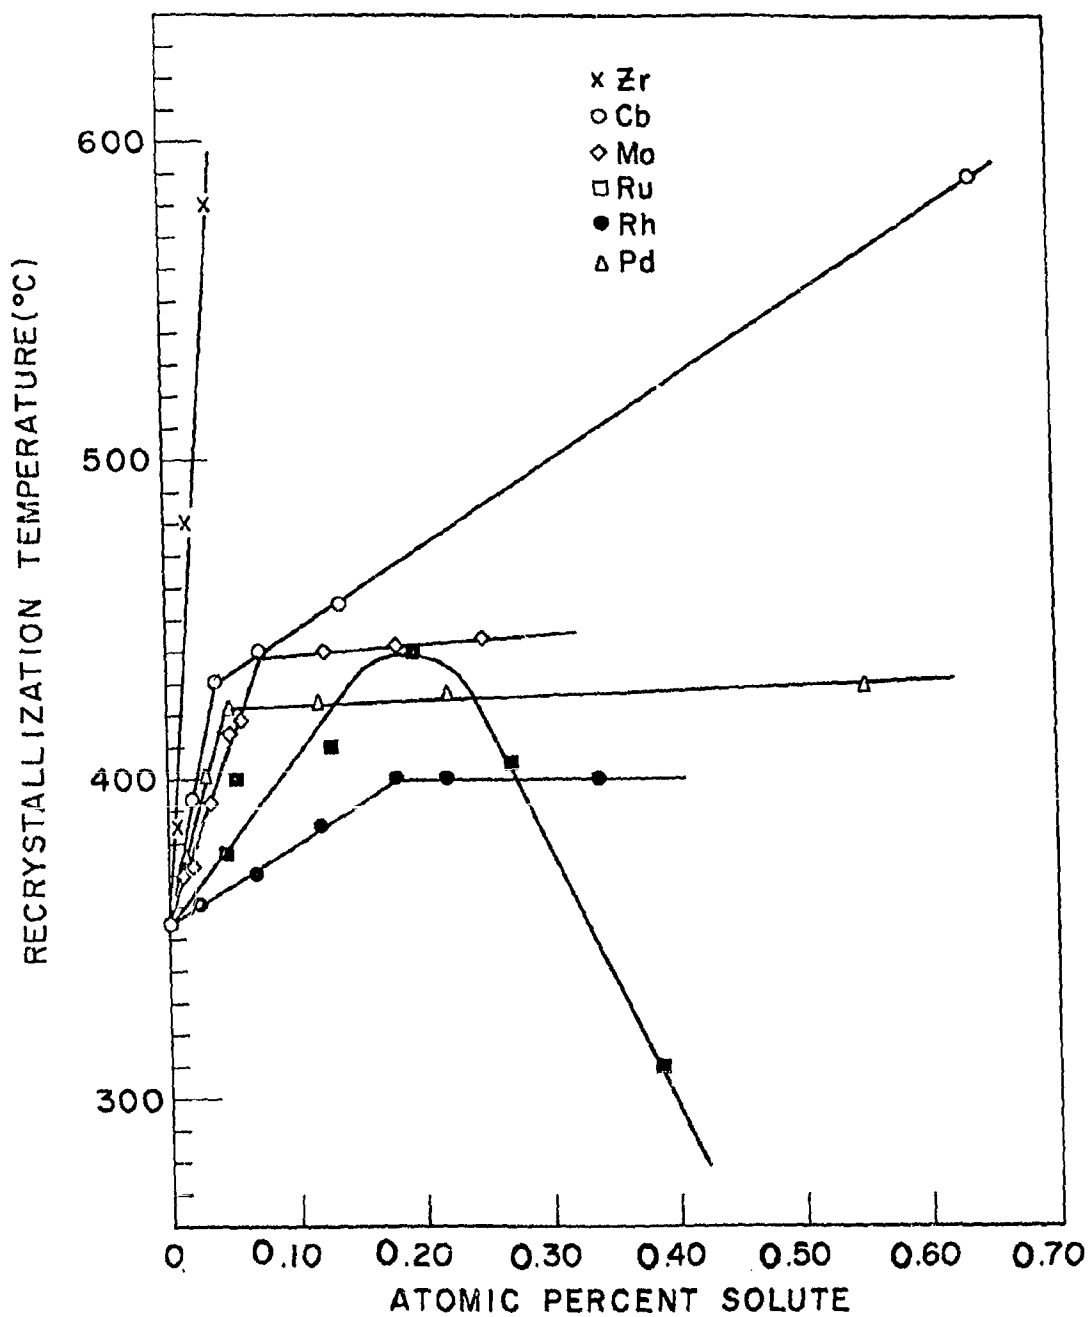


RECRYSTALLIZATION TEMPERATURE VERSUS ATOMIC PERCENT SOLUTE FOR THE SECOND TRANSITION SERIES.

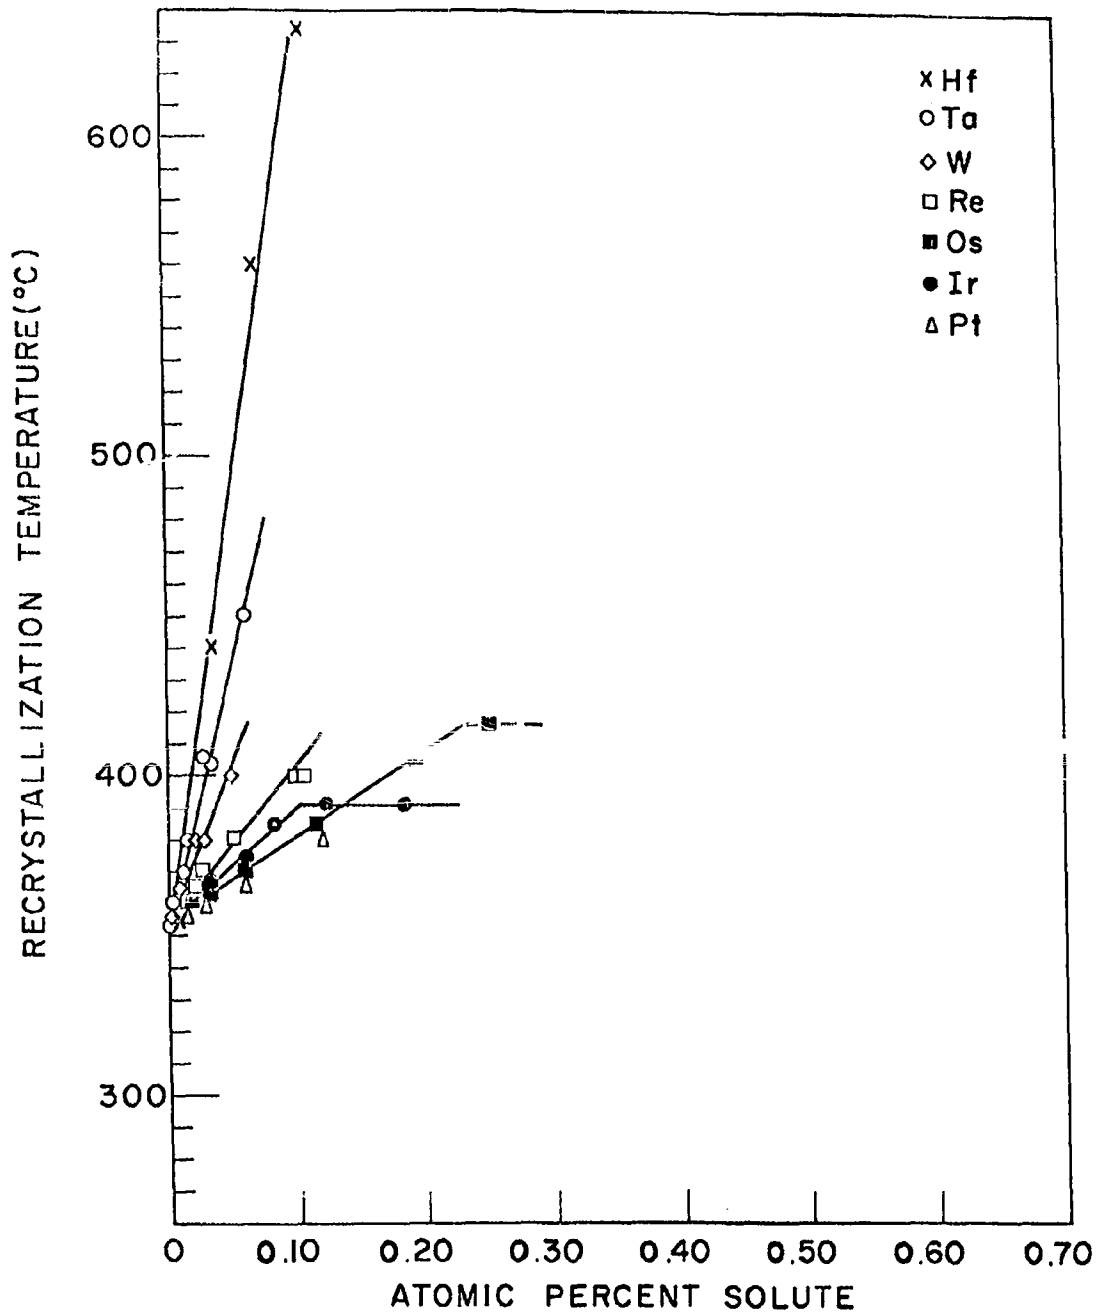

RECRYSTALLIZATION TEMPERATURE VERSUS ATOMIC PERCENT SOLUTE FOR THE THIRD TRANSITION SERIES.

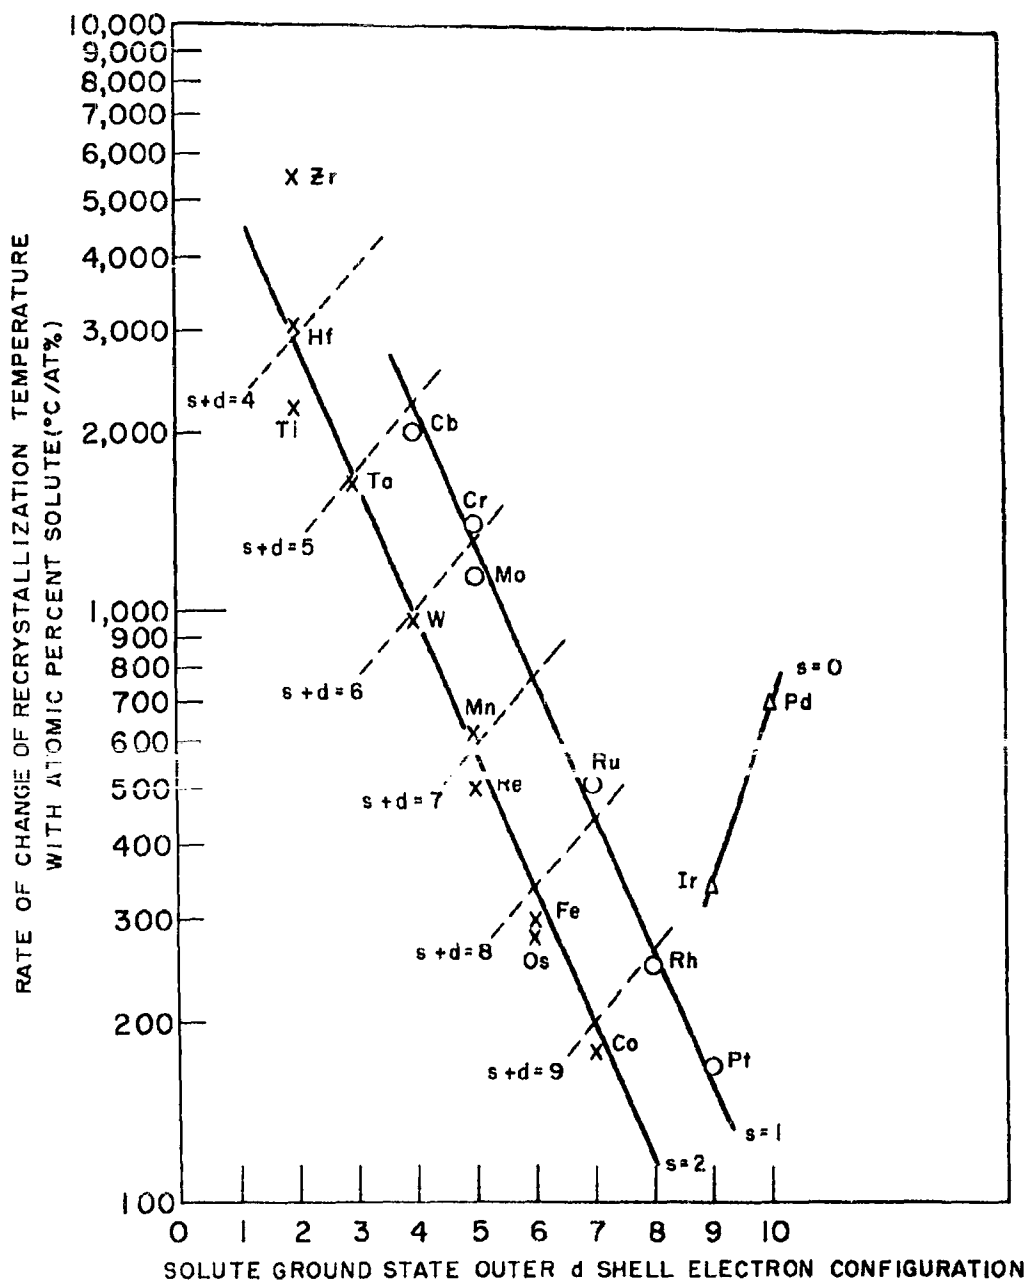

RATE OF CHANGE OF RECRYSTALLIZATION TEMPERATURE WITH ATOMIC PERCENT SOLUTE VS GROUND STATE OUTER ELECTRON CONFIGURATION OF SOLUTE.

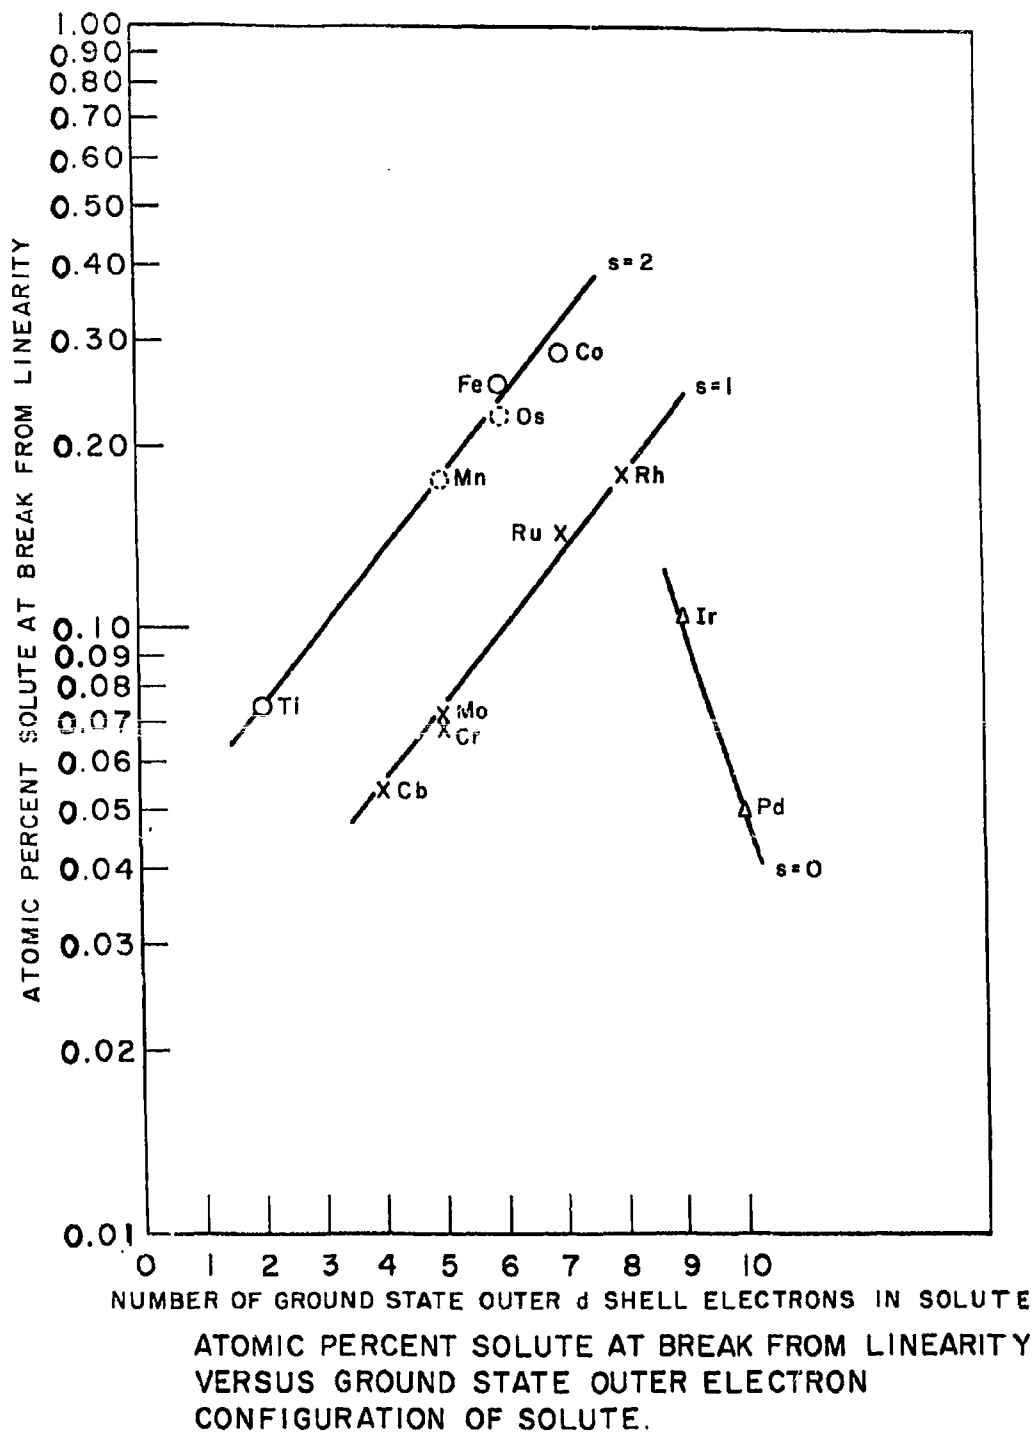

REFERENCES

1. ABRAHAMSON, E. P., II, and GRANT, N. J., Brittle to Ductile Transition of Binary Chromium-Base Alloys, Transactions, A.S.M., v. 50, 1958, p. 705-721.
2. ABRAHAMSON, E. P., II, and BLAKENEY, B. S., JR., The Effect of Dilute Transition Element Additions on the Recrystallization of Iron, Transactions of the Metallurgical Society, AIME, v. 218, 1960, p. 1101-1104.
3. ABRAHAMSON, E. P., II, The Recrystallization of Iron as a Function of Binary Solute Additions and Time, Watertown Arsenal Laboratories, WAL TR 830.3/2, January 1961.
4. ABRAHAMSON, E. P., II, The Role of Dilute Binary Transition Element Additions on the Recrystallization of Vanadium, Watertown Arsenal Laboratories, WAL TR 830.3/3, July 1961.
5. ABRAHAMSON, E. P., II, The Role of Dilute Binary Transition Element Additions on the Recrystallization of Columbium, Watertown Arsenal Laboratories, WAL TR 830.3/4, July 1961.
6. ABRAHAMSON, E. P., II, The Role of Dilute Binary Transition Element Additions on the Recrystallization of Zirconium, Watertown Arsenal Laboratories, WAL TR 830.3/5, July 1961.
7. ABRAHAMSON, E. P., II, The Role of Dilute Binary Transition Element Additions on the Recrystallization of Titanium, Watertown Arsenal Laboratories, WAL TR 830.3/6, November 1961.
8. OLSEN, K. M., The Effect of Trace Elements on the Tensile, Electrical Resistance and Recrystallization Properties of High Purity Nickel, Transactions, A.S.M., v. 52, 1960, p. 545-558.
9. HANSEN, M., Constitution of Binary Alloys, McGraw-Hill Book Co.; New York, 1958.
10. KITTEL, C., Introduction of Solid State Physics, John Wiley & Son, Inc., New York, 2nd Ed., 1956, p. 66.

No. of
Copies

TO

1 Commanding General, U. S. Army Rocket and Guided Missile Agency,
Redstone Arsenal, Alabama
ATTN: ORDAB-DV

5
1 ORDXR-RGA, Mr. R. L. Wetherington
1 ORDXR-RMO, Lt. E. J. Wilson

1 Commanding Officer, Detroit Arsenal, Center Line, Michigan
ATTN: ORDMX-BMW

1 ORDMX-AL

1 Commanding Officer, Diamond Ordnance Fuze Laboratories,
Washington 25, D. C.
ATTN: ORDTL .012, Technical Reference Branch

2 Commanding Officer, Frankford Arsenal, Philadelphia 37, Pennsylvania
ATTN: Pitman-Dunn Laboratories

1 Commanding Officer, Ordnance Materials Research Office,
Watertown Arsenal, Watertown 72, Massachusetts
ATTN: RPD

1 Commanding Officer, Picatinny Arsenal, Dover, New Jersey
ATTN: Feltman Research Laboratories

1 Commanding Officer, Rock Island Arsenal, Rock Island, Illinois
ATTN: Laboratory

1 Commanding Officer, Springfield Armory, Springfield 1, Massachusetts
ATTN: ORDBD-TX

1 Commanding Officer, Watervliet Arsenal, Watervliet, New York
ATTN: ORDBF-RT

1 Chief, Bureau of Ships, Department of the Navy, Washington 25, D. C.
ATTN: Code 341

1 Chief, Bureau of Naval Weapons, Department of the Navy, Room 2225,
Munitions Building, Washington 25, D. C.
ATTN: RMMP

1 Chief, Office of Naval Research, Department of the Navy,
Washington 25, D. C.
ATTN: Code 423

1 Chief, Naval Engineering Experimental Station, Department of the
Navy, Annapolis, Maryland

No. of
Copies

TO

1 Commander, Naval Ordnance Test Station, China Lake, California
ATTN: Code 5557

1 Director, Naval Research Laboratory, Anacostia Station,
Washington, D. C.
ATTN: Technical Information Officer

1 Commander, Naval Weapons Laboratory, Dahlgren, Virginia
ATTN: A & P Laboratory

5 Commander, Wright Air Development Division, Wright-Patterson
Air Force Base, Ohio
ATTN: WWRCEE

15 U. S. Atomic Energy Commission, Office of Technical Information
Extension, P. O. Box 62, Oak Ridge, Tennessee

1 Army Reactor Branch, Division of Research Development,
Atomic Energy Commission, Washington 25, D. C.

1 National Aeronautics and Space Administration, 1520 H Street, N. W.,
Washington 25, D. C.

1 Director, Jet Propulsion Laboratory, California Institute of
Technology, Pasadena 3, California
ATTN: Dr. L. Jaffe

5 Dr. W. R. Lucas, George C. Marshall Space Flight Center,
Huntsville, Alabama
ATTN: M-S&M-M

1 Mr. W. A. Wilson, George C. Marshall Space Flight Center,
Huntsville, Alabama
ATTN: M-F&AE-M, Building 4720

1 Defense Metals Information Center, Battelle Memorial Institute,
Columbus, Ohio

5 Commanding Officer, Watertown Arsenal, Watertown 72, Massachusetts
ATTN: ORDBE-LXM, Technical Information Section

1 Author

83 -- TOTAL COPIES DISTRIBUTED

AD Accession No.
Watertown Arsenal Laboratories, Watertown 72, Mass.
THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS ON THE
RECRYSTALLIZATION OF NICKEL - Ernest P. Abrahamson, II
Report No. WAL TR 830.3/7, Nov 1961, 12 pp - illus,
OMS Code 5010.11.8050051, D/A Proj 5893-32-001,
Unclassified Report

The effect of transition element binary solid solution additions upon the recrystallization temperature of nickel has been investigated. All additions raised the recrystallization temperature. Both the rate of change of recrystallization temperature with atomic percent solute and the limit of initial linearity are found to correlate with the free atom ground state outer electron configuration of the solute element.

NO DISTRIBUTION LIMITATIONS

UNCLASSIFIED

1. Recrystallization
2. Transition elements
3. Nickel
- I. Abrahamson, Ernest P., II
- II. OMS Code 5010.11.8050051
- III. D/A Proj 5893-32-001

AD Accession No.
Watertown Arsenal Laboratories, Watertown 72, Mass.
THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS ON THE
RECRYSTALLIZATION OF NICKEL - Ernest P. Abrahamson, II
Report No. WAL TR 830.3/7, Nov 1961, 12 pp - illus,
OMS Code 5010.11.8050051, D/A Proj 5893-32-001,
Unclassified Report

The effect of transition element binary solid solution additions upon the recrystallization temperature of nickel has been investigated. All additions raised the recrystallization temperature. Both the rate of change of recrystallization temperature with atomic percent solute and the limit of initial linearity are found to correlate with the free atom ground state outer electron configuration of the solute element.

NO DISTRIBUTION LIMITATIONS

UNCLASSIFIED

1. Recrystallization
2. Transition elements
3. Nickel
- I. Abrahamson, Ernest P., II
- II. OMS Code 5010.11.8050051
- III. D/A Proj 5893-32-001

AD Accession No.
Watertown Arsenal Laboratories, Watertown 72, Mass.
THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS ON THE
RECRYSTALLIZATION OF NICKEL - Ernest P. Abrahamson, II
Report No. WAL TR 830.3/7, Nov 1961, 12 pp - illus,
OMS Code 5010.11.8050051, D/A Proj 5893-32-001,
Unclassified Report

The effect of transition element binary solid solution additions upon the recrystallization temperature of nickel has been investigated. All additions raised the recrystallization temperature. Both the rate of change of recrystallization temperature with atomic percent solute and the limit of initial linearity are found to correlate with the free atom ground state outer electron configuration of the solute element.

NO DISTRIBUTION LIMITATIONS

UNCLASSIFIED

1. Recrystallization
2. Transition elements
3. Nickel
- I. Abrahamson, Ernest P., II
- II. OMS Code 5010.11.8050051
- III. D/A Proj 5893-32-001

AD Accession No.
Watertown Arsenal Laboratories, Watertown 72, Mass.
THE ROLE OF DILUTE BINARY TRANSITION ELEMENTS ON THE
RECRYSTALLIZATION OF NICKEL - Ernest P. Abrahamson, II
Report No. WAL TR 830.3/7, Nov 1961, 12 pp - illus,
OMS Code 5010.11.8050051, D/A Proj 5893-32-001,
Unclassified Report

The effect of transition element binary solid solution additions upon the recrystallization temperature of nickel has been investigated. All additions raised the recrystallization temperature. Both the rate of change of recrystallization temperature with atomic percent solute and the limit of initial linearity are found to correlate with the free atom ground state outer electron configuration of the solute element.

NO DISTRIBUTION LIMITATIONS

UNCLASSIFIED

1. Recrystallization
2. Transition elements
3. Nickel
- I. Abrahamson, Ernest P., II
- II. OMS Code 5010.11.8050051
- III. D/A Proj 5893-32-001