

UNCLASSIFIED

AD 272 094

*Reproduced
by the*

**ARMED SERVICES TECHNICAL INFORMATION AGENCY
ARLINGTON HALL STATION
ARLINGTON 12, VIRGINIA**



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

GIIIIID

272094

REPORT NO: FTD-2690
DATE: JANUARY 30, 1962

62-2-3

XEROX

FILLER METAL, ELECTRODE AND FILLER WIRE FOR
SAE 4340 STEEL, 260-292 KSI HEAT TREAT RANGE,
EVALUATION OF

Published and Distributed Under
Contract AF33(657)-7248

GENERAL DYNAMICS | FORT WORTH

TEST DATA MEMORANDUM

F-TDM NO. 2690
MODEL B-58
TEST NO. F-8143

TEST: Filler Metal, Electrode and Filler Wire For SAE 4340 Steel, 260-292 KSI Heat Treat Range, Evaluation Of

OBJECT: Determine from tensile and hardness tests of welds in SAE 4340 steel which of six candidate electrodes and filler wires will provide welds heat treatable to the 260-292 KSI strength level.

Test Specimens & Procedure: Weldments for the evaluation tests were made using P & H 4340, BA 91, and Airco Special Electrodes and Oxweld 71, Oxweld MW, and A 613 filler wires.

Welding was done by Convair production welders. The plates for welding were preheated to approximately 450 F and maintained at this temperature during and after welding until stress relieved at 1150 F. Before sectioning for specimens, the welded plates were magnaflux and X-ray inspected.

Transverse tensile specimens and all-weld-metal tensile specimens were obtained from the butt welded plates as shown in Figures 1 and 2, respectively. All the specimens were heat treated by heating to 1550 F, holding 30 minutes, quenching in oil, and double tempering for 2 hours at 400 F. Following heat treatment, the specimens were finish machined to size. The testing was conducted on a 120,000 pound capacity Baldwin universal test machine*.

Results: Test results are tabulated in Tables I and II.

Discussion: The strength range of (260-292) ksi was not consistently obtained with any of the electrodes or filler wires evaluated. Weld joint efficiencies of over 90% or 245 ksi were obtained with both the P & H 4340 electrode and the Oxweld 71 filler wire. Both of these welding materials exhibited very good ductility as measured by percent elongation and reduction of area.

Two of the electrodes evaluated in the transverse weld tests were experimental and only available in limited quantities, and therefore, were not tested as all-weld specimens. The brittle fractures that were obtained with the Oxweld MW filler wire eliminated it from further consideration.

Conclusion: None of the candidate filler materials consistently provided welds in the 260-292 ksi strength range in 4340 plate.

*Strain rate was approximately .003 in./in./min. thru yield.

WITNESS:

DATE 9/6/60

BY

CHECKED

APPROVED

Don for C Wilson

CONVAIR

A DIVISION OF GENERAL DYNAMICS CORPORATION
(FORT WORTH)

PAGE 2
REPORT NO. ETDN No. 2690
MODEL B-58
DATE 9/6/60

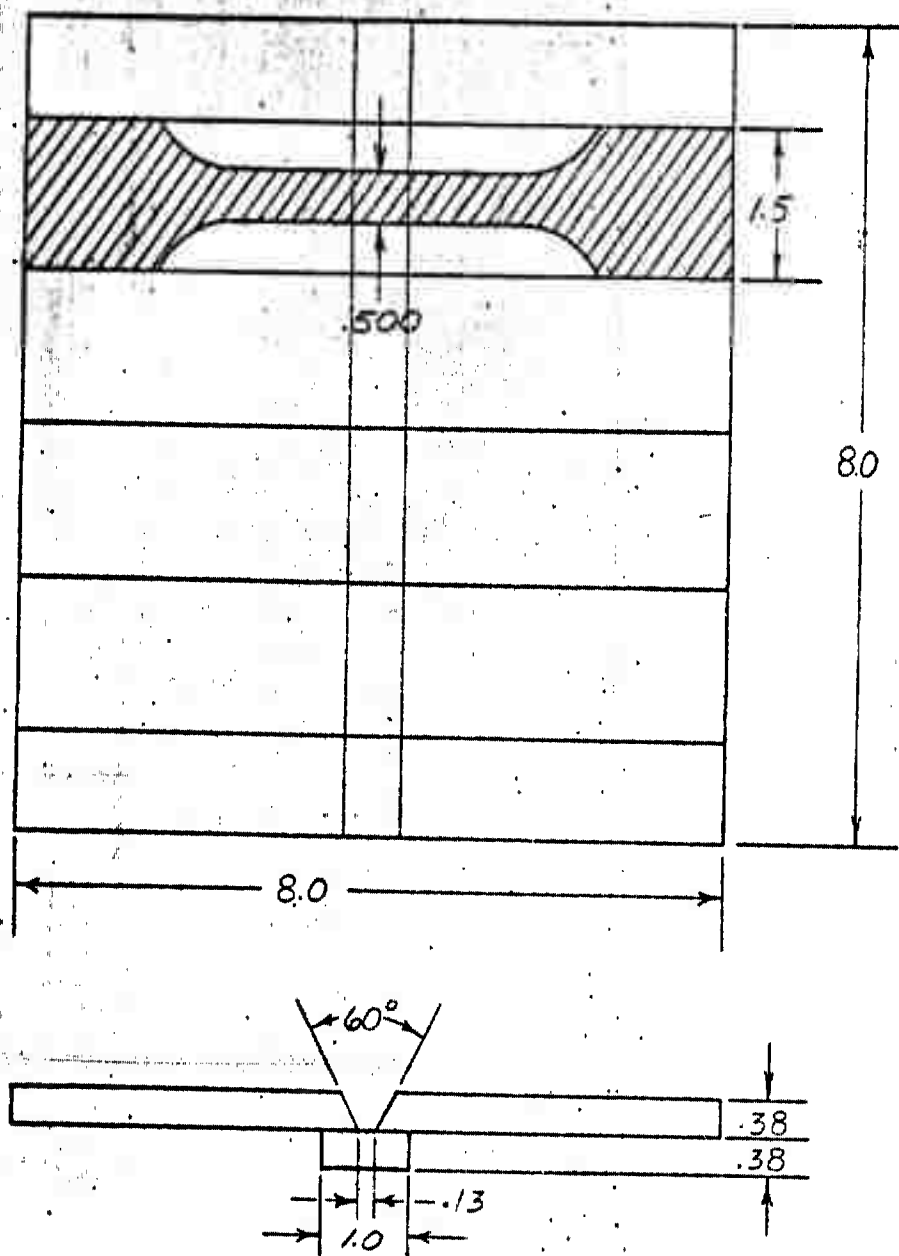


FIG. 1 - TRANSVERSE TENSILE WELDMENT
AND SPECIMEN DIMENSIONS.

CONVAIR

A DIVISION OF GENERAL DYNAMICS CORPORATION
(FORT WORTH)

PAGE 3
REPORT NO. F T D M 2690
MODEL B-58
DATE 9/6/60

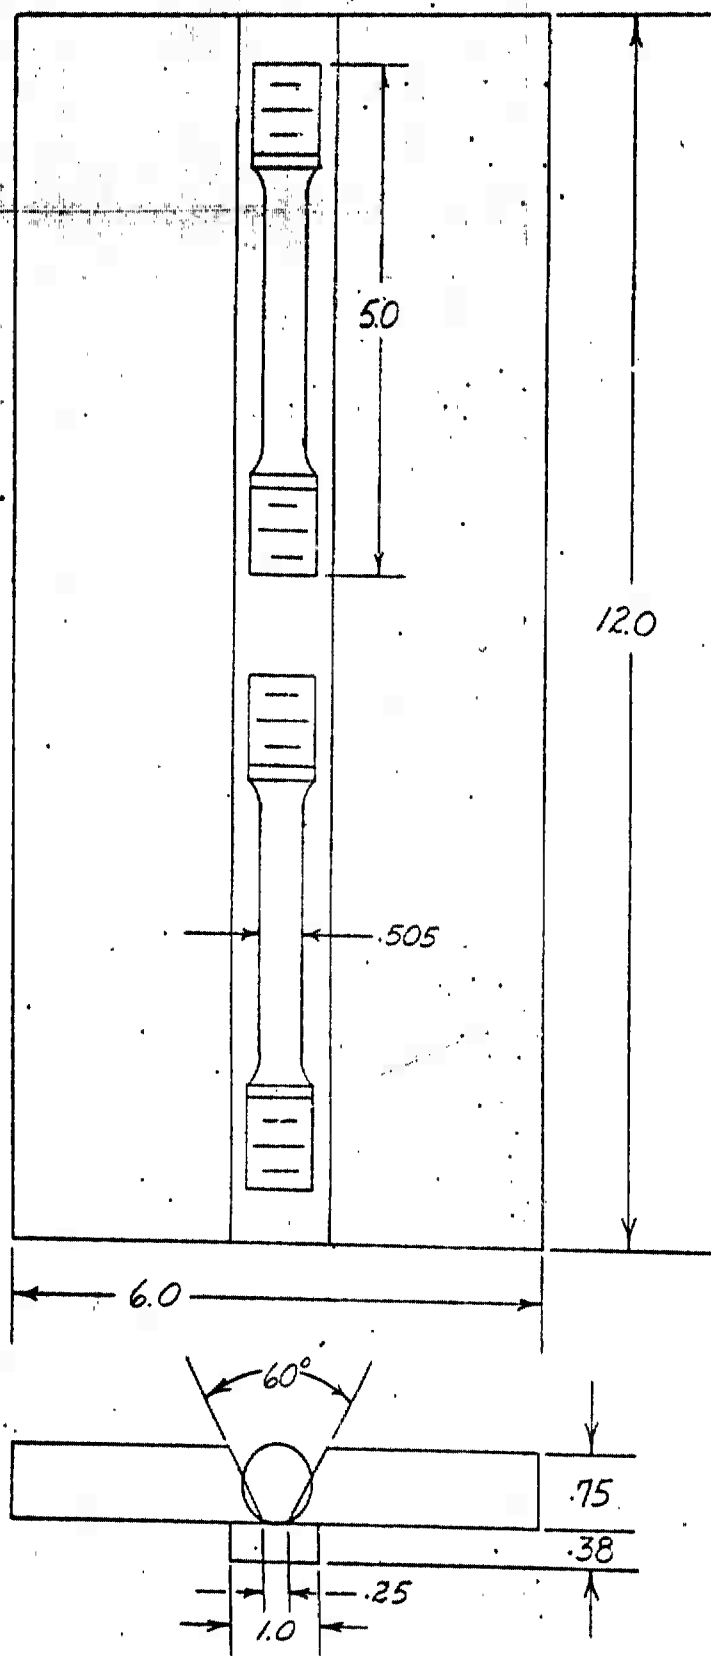


FIG. 2 - ALL-WELD-METAL SPECIMEN LOCATION.

[illegible]

BASE MATERIAL	FILLER MATERIAL	UTS (KSI)	YTS (KSI)	2" GAGE LOCATION	HEAT TREAT RANGE	CONV. (KSI)
4340 STL	BNH 4340	249.6	229.7	2.5 W		
	FLEC.	244.6	227.4	6.5 W		
		244.1	234.0	2.5 W		
AVG.		252.8	230.4	3.8	52.0	273.0
4340 STL	BAGI	257.7	221.6	11.0 W		
	FLEC.	254.9	216.0	5.5 W		
		262.7	219.5	5.0 W		
AVG.		258.4	219.0	7.2	52.0	273.0
4340 STL	AIRCO SPECIAL	252.6	-	6.0 W		
	FLEC.	253.5	-	7.0 W		
		254.5	-	4.0 W		
AVG.		253.5	-	5.7	52.0	273.0
4340 STL	OKWELD 71	246.9	203.5	9.0 W		
	3/32 WIRE	251.8	221.1	7.0 W		
		244.7	210.8	7.0 W		
AVG.		247.8	212.5	7.7	52.0	273.0
4340 STL	AG13	246.5	-	4.0 W		
	3/32 WIRE	236.3	-	7.5 W		
		248.4	-	5.5 W		
AVG.		243.7	-	5.7	52.0	273.0
4340 STL	OKWELD 71	237.1	-	1.5 W		
	3/32 WIRE	250.2	-	2.0 W		
		214.4	-	1.5 W		
AVG.		233.9	-	1.7	52.0	273.0

CONVAIR — FORT WORTH

TABLE II

TABULATION SHEET MECHANICAL PROPERTIES OF ALL-WELD METAL TENSILE SPECIMENS

BASE MATERIAL	FILLER METAL	FILLER FORM	UTS (KSI)	YTS (KSI)	260-292 KSI % ELONG.	2" GAGE R _g	HEAT TREAT DIL. COEFF. (KSI)	RANGE % R.A.	TENSILE SPECIMENS
4340 STL	pin 4340	3/32 ROD	246.5	199.0	4.5			11.1	
			254.5	202.9	7.0			11.5	
			258.2	206.2	7.5			29.3	
AVG.			245.5	200.0	8.0			29.5	
			251.2	202.0	6.8	49.0	246.0	20.6	
4340 STL	pin 4340	1/8 ROD	271.4	-	8.0			34.1	
			260.0	-	4.5			10.0	
			260.0	-	8.0			36.0	
AVG.			260.7	-	6.5			18.6	
			263.0	-	6.8	51.5	268.0	24.7	
4340 STL	pin 4340	1/32 ROD	259.7	-	8.0			37.1	
			267.1	214.5	5.5			32.6	
			262.2	200.1	8.0			29.3	
AVG.			255.2	204.4	8.0			33.5	
			261.1	206.3	7.4	49.5	251.0	53.1	
4340 STL	ONWELD WIRE (3/32)		251.7	222.2	5.0			34.7	
			251.5	221.0	5.0			37.3	
			252.5	220.9	5.0			40.5	
AVG.			253.7	222.7	5.0			36.0	
			252.4	221.7	5.0	49.5	251.0	57.1	
4340 STL	A613	WIRE (3/32)	246.1	222.4	5.0			44.0	
			243.7	217.7	7.0			53.9	
			245.7	219.7	7.0			51.8	
AVG.			247.8	222.7	7.0			50.8	
			245.8	221.2	6.5	48.5	242.0	50.1	

UNCLASSIFIED

UNCLASSIFIED