

**UNCLASSIFIED**

---

---

**AD 299 673**

*Reproduced  
by the*

**ARMED SERVICES TECHNICAL INFORMATION AGENCY  
ARLINGTON HALL STATION  
ARLINGTON 12, VIRGINIA**



---

---

**UNCLASSIFIED**

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

63-3-1

FTD-TT-62-1735

ASTIA 299673

ASTIA

AD AD IND

# TRANSLATION

HYDROPURIFICATION OF A REFINED DIESEL OIL

By


R. Sh. Kuliyeu and B. A. Sadykhova

## FOREIGN TECHNOLOGY DIVISION

AIR FORCE SYSTEMS COMMAND

WRIGHT-PATTERSON AIR FORCE BASE

OHIO

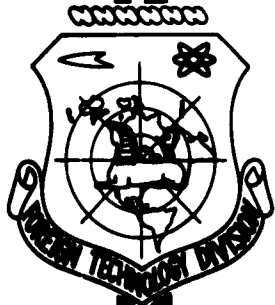

ASTIA  
RECEIVED  
APR 8 1963  
TISIA

## UNEDITED ROUGH DRAFT TRANSLATION

HYDROPURIFICATION OF A REFINED DIESEL OIL

By: R. Sh. Kuliyeu and B. A. Sadykhova

English Pages: 5

Source: Khimiya i Tekhnologiya Topliv i  
Masel, No. 5, 1962, pp. 32-34.

SOV/65-62-0-5-1/2

THIS TRANSLATION IS A RENDITION OF THE ORIGINAL FOREIGN TEXT WITHOUT ANY ANALYTICAL OR EDITORIAL COMMENT. STATEMENTS OR THEORIES ADVOCATED OR IMPLIED ARE THOSE OF THE SOURCE AND DO NOT NECESSARILY REFLECT THE POSITION OR OPINION OF THE FOREIGN TECHNOLOGY DIVISION.

PREPARED BY:

TRANSLATION SERVICES BRANCH  
FOREIGN TECHNOLOGY DIVISION  
OF AFS, OND.

## HYDROPURIFICATION OF A REFINED DIESEL OIL

R. Sh. Kuliyeu and B. A. Sadykhova

A complex of scientific research projects has recently been completed at the Institute of Petrochemical Processes of the Academy of Sciences of the Azerbaidzhan SSR for the purpose of making fundamental improvement in the quality of oils produced at the Baku factories.

The use of the hydrogenation method for additional purification of distillate oils was of particular concern in these projects.

The original distillate of D-11 diesel oil from a mixture of Baku nonparaffinic petroleums and a refined oil obtained by purification of this distillate with 250% furfurool were subjected to hydrogenation.

The present article deals with the results of hydropurification of a refined diesel oil in place of acid-contact repurification.

The hydrogenation was performed in a pilot apparatus with a 200 cm<sup>3</sup> catalyst charge in the reactor and a constant hydrogen flow of 30 liters/hr. The industrial catalysts Al-Co-Mo and WS<sub>2</sub> were used as the catalysts, after the tablets and granules were pulverized to a

crumb size of 1.0-1.5 mm.

The hydropurification was carried out at feed rates of 0.3, 0.5, and 1.0 m<sup>3</sup>/m<sup>3</sup> of raw material to the catalyst loaded in the reactor at various temperatures and pressures. The results of experiments conducted with a raw-material supply of 0.5 m<sup>3</sup>/m<sup>3</sup> with temperatures in the range from 300-400°C and pressures from 50-200 atm (tech) are described below (Table 1).

TABLE 1  
Hydropurification of Refined D-11 Diesel Oil with Al-Co-Mo Catalyst

Conditions of hydropurification		Characteristics of refined oil and purified oil										
Temperature, °C	Pressure, atm (tech)	Density, g/cm <sup>3</sup> at 20	Viscosity at 100°C, es	Viscosity ratio, 50/100	Viscosity Index	Viscosity-kinematic constant	Acid number, mg/KOH	Sinking capacity, %	Flash point in open crucible, °C	Color according to NPA, grade	Corrosion according to Pinkovich method, g/m <sup>2</sup>	Stability according to the method of the Azerbaijan Scientific Research Institute, min
Original refined oil		0.900	11.20	6.50	60.0	0.840	0.02	0.14	226	dark	—	60
300	50	0.900	11.20	6.50	63.0	0.840	0.02	0.10	220	5	1.90	110
300	100	0.899	11.0	6.40	63.0	0.840	0.02	0.10	220	4 1/2	1.90	118
300	150	0.8965	10.60	6.40	65.0	0.839	0.02	0.08	216	3 1/2	1.00	120
350	50	0.8967	10.93	6.20	66.6	0.8352	0.013	0.010	218	4	—	159
350	100	0.8968	10.57	6.22	68.0	0.8360	0.010	0.040	214	2	—	177
350	150	0.8963	10.54	6.28	68.0	0.8358	0.012	0.050	210	1 1/2	0.540	188
350	200	0.8960	10.52	6.20	68.0	0.8360	0.018	0.048	210	1 1/2	—	190
400	150	0.8919	8.5	5.39	78.0	0.8310	0.01	0.02	150	1 1/2	1.84	181
		0.9000	10.56	6.30	62.0	0.8390	0.02	0.12	225	4 1/2	5.00	230
Oil purified by acid-contact method												

It is apparent from Table 1 that at a temperature of 300°C and a pressure of 50 atm (tech) the quality of the hydropurified oil, in comparison with the original refined oil, is not altered significantly, save for a certain improvement in stability and color.

In comparison with the acid-contact repurification oil, the hydropurified oil is less corrosive and half as stable, as determined by the method of the ASRI.

An increase in pressure to 100 and 150 atm (tech) at a constant temperature of 300°C leads to a certain improvement in the quality of

the refined oil: the viscosity index increases somewhat, and the color improves to a grade of 3 1/2. An increase in the temperature of the hydropurification process from 300° to 350°C at a constant pressure of 50 atm (tech) also leads to a certain improvement in the quality of the refined oil. This oil with respect to all indices, except stability, according to the method of the ASRI, surpasses the oil of acid-contact repurification.

The quality of the oil is considerably improved after hydropurification at a pressure of 100 to 150 atm (tech) and a temperature of 350°C.

Oil obtained under these conditions gives the best indices with respect to density, viscosity-weight constant, coking capacity, color, stability, and viscosity index. A further increase in pressure from 150 to 200 atm (tech) has almost no effect on the quality of the refined oil.

An increase in the temperature of the hydropurification to 400°C (cf. Table 1) leads to appreciable destruction of the raw material, as a result of which the viscosity of the refined product is reduced to 8.5 cs, while the flash point is reduced to 150°C.

The results of hydropurification of a refined diesel oil with a WS<sub>2</sub> catalyst are presented in Table 2.

It is apparent from the data in Table 2 that hydropurification of a refined oil in the presence of a WS<sub>2</sub> catalyst proceeds satisfactorily at a temperature of 300°C and a pressure of 50 atm (tech). When the pressure is increased from 50 to 150 atm (tech), the quality of the refined oil is improved. A further increase in the pressure of the process to 200-250 atm (tech) leads to a slight improvement in the qualities of the refined oil.

TABLE 2

Hydropurification of Refined D-11 Diesel Oil with a WS<sub>2</sub>  
Catalyst

Conditions of hydropurification			Characteristics of refined oil and purified oil											
Temperature, °C	Pressure, atm (tech)	Feed rate of raw material, m <sup>3</sup> /h	Density, g/cm <sup>3</sup>	Viscosity at 100°C, cSt	Viscosity ratio %50/100	Viscosity index	Viscosity-weight constant	Acid number, mg/100g	Sulfur content, %	Flash point in open apparatus, °C	Flash point in closed apparatus, °C	Water content, %	Corrosion according to Pinkovich test, g/m <sup>2</sup>	Stability according to the standard of the Azerbaijan Scientific Research Institute, min
Original refined oil			0.900	11.20	6.50	60.0	0.840	0.020	0.14	226	1	Greater than 8	—	50
300	50	0.5	0.900	11.00	6.40	64.0	0.840	0.020	0.050	214	1	4	1.50	103
300	100	0.5	0.897	10.90	6.20	65.0	0.839	0.020	0.048	212	1.2	3 1/2	1.50	110
300	150	0.5	0.896	10.80	6.20	66.4	0.839	0.020	0.048	212	1.0	2*	1.046	178
300	200	0.5	0.896	10.60	6.10	66.6	0.836	0.015	0.046	210	1.2	3*	1.03	156
300	250	0.5	0.892	9.50	5.80	68.0	0.836	0.012	0.042	200	1.2	3*	—	190
350	100	0.5	0.861	4.30	3.60	100.0	0.810	0.010	0.027	60*	1.7	1 1/2	—	—

\* Flash point in closed apparatus

Diesel oil obtained by hydropurification of a refined oil with a WS<sub>2</sub> catalyst is not corrosive.

In the case of both the Al-Co-Mo catalyst and the WS<sub>2</sub> catalyst the yield of finished oil was 95%-98% of the original refined oil.

### Conclusions

1. Preliminary investigations have established the possibility of replacing contact-acid repurification of a refined diesel oil from a mixture of Baku nonparaffinic petroleums by hydropurification with the industrial catalysts Al-Co-Mo and WS<sub>2</sub>.

2. Hydropurification with Al-Co-Mo catalysts at a temperature of 350°C and a pressure of 50 atm (tech) allows us to obtain a diesel oil with somewhat better physicochemical properties than the corresponding oil obtained by repurification of the refined oil with 1% sulfuric acid and 5% clay. Hydropurification carried out at pressures greater than 50 atm (tech) [100-150 atm (tech)] allows us to obtain oils of considerably better quality than acid-contact repurification oils.

3. It has been established that the  $WS_2$  catalyst has a greater hydrogenating capacity than the Al-Co-Mo catalyst. However, an increase in temperature above  $300^\circ C$  leads to cracking in the presence of  $WS_2$ .

Institute of Petrochemical Processes  
of the Academy of Sciences of the  
Azerbaijan SSR

DISTRIBUTION LIST

DEPARTMENT OF DEFENSE	Nr. Copies	MAJOR AIR COMMANDS	Nr. Copies
		AFSC	
		SCFDD	1
		ASTIA	25
HEADQUARTERS USAF		TDBTL	5
		TDBDP	5
AFPCIN-3D2	1	SSD (SSF)	2
ANL (ARR)	1	BSD (BSF)	1
		AFFTC (FTY)	1
OTHER AGENCIES			
OIA	1		
NSA	1		
NSA	1		
NSA	1		
ONS	1		
NSC	1		
PAS	1		
NSA	1		
DIA	9		
NAVY	3		
ARMY	3		
PGE	12		
RAND	1		