

UNCLASSIFIED

AD NUMBER	
AD368227	
CLASSIFICATION CHANGES	
TO:	UNCLASSIFIED
FROM:	CONFIDENTIAL
LIMITATION CHANGES	
TO: Approved for public release; distribution is unlimited.	
FROM: Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative/Operational Use; MAR 1965. Other requests shall be referred to Rocket Propulsion Lab., Edwards AFB, CA.	
AUTHORITY	
31 Mar 1977, DoDD 5200.10 ; RPL per DTIC form 55	

THIS PAGE IS UNCLASSIFIED

SECURITY

MARKING

The classified or limited status of this report applies to each page, unless otherwise marked.

Separate page printouts MUST be marked accordingly.

THIS DOCUMENT CONTAINS INFORMATION AFFECTING THE NATIONAL DEFENSE OF THE UNITED STATES WITHIN THE MEANING OF THE ESPIONAGE LAWS, TITLE 18, U.S.C., SECTIONS 793 AND 794. THE TRANSMISSION OR THE REVELATION OF ITS CONTENTS IN ANY MANNER TO AN UNAUTHORIZED PERSON IS PROHIBITED BY LAW.

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

**Best
Available
Copy**

CONFIDENTIAL

AFRPL-TR-65-57

368227

(Unclassified Title)


**FEASIBILITY DEMONSTRATION
OF PYROLYTIC GRAPHITE COATED NOZZLES**

TECHNICAL REPORT NO. AFRPL-TR-65-57

March 1965

**U.S. Air Force
Air Force Systems Command
Rocket Propulsion Laboratory
Edwards, California**

Project No. 3059, Task No. 03

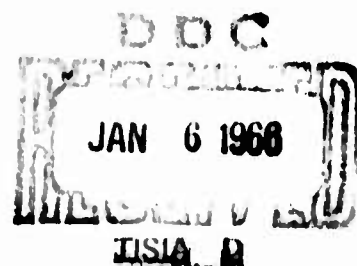

**(Prepared under Contract No. AF 04(611)-9708 by the
Atlantic Research Corporation, Alexandria, Virginia;
J. D. Batchelor, E. F. Ford, and E. L. Olcott, Authors)**

**GROUP 4
DOWNGRADED AT 3 YEAR INTERVALS
DECLASSIFIED AFTER 12 YEARS
DOD DIR 5200-10**

CONFIDENTIAL

COPY NO.

ESPIONAGE CLAUSE

This document contains information affecting the national defense of the United States within the meaning of the Espionage Acts, Title 18, U.S.C., Sections 793 and 794. The transmission or the revelation of its contents in any manner to an unauthorized person is prohibited by law.

AFRPL-TR-65-57

FOREWORD

This report was prepared by Atlantic Research Corporation to document all work performed under Air Force Contract AF 04(611)-9708 from 2 February 1964 to 4 March 1965. This work was administered under the direction of the Air Force Rocket Propulsion Laboratory, Edwards, California. Lt. Robert Schoner was the Air Force Project Officer.

Dr. James D. Batchelor was responsible for the administrative and technical aspects of the program. The over-all program was carried out under Mr. Eugene L. Olcott, Director, Materials Division.

The secondary report number assigned to this report by the contractor is TR-PL-6839-01-0.

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILMED.

AFRPL-TR-65-57

(This abstract is Unclassified)

ABSTRACT

Pyrolytic graphite coatings have been found to be highly erosion resistant under severe rocket nozzle conditions. The objective of this program was to demonstrate the feasibility of such coatings for nozzles up to 2.3-inch diameter in firings at 700 psi with a 6550°F propellant. This objective was accomplished.

Stress analyses and thermal analyses were carried out in support of the design, fabrication, and motor testing of nozzles of both 1.1-inch and 2.3-inch diameter. Thermal analysis indicated the potential of pyrolytic graphite coatings for lightweight nozzle designs. The results of the stress analyses for coated composites were correlated with experimental evidence of delamination cracking in the coatings. Critical stress levels were identified for both radial tension in the coating and axial tension in the substrate. The deposition process was improved to produce crack-free coatings 50-mil thick on conventional graphite substrates and 100-mil thick on a fibrous graphite substrate.

Nine motor firing tests were made and good performance was demonstrated with both subscale and full-scale nozzles. The presence of microscopically observed delamination cracks was found to destroy the integrity of pyrolytic graphite coatings during nozzle service. For coatings without major cracks coating integrity was achieved, however, and erosion rates of acceptable magnitude were measured for subscale nozzles for durations up to about 40 seconds. In full-scale nozzles satisfactory erosion rates were measured for firings of durations up to 60 seconds. Optimization of the coating to provide minimum erosion rates should result in still further performance improvements.

To test the restart capability of pyrolytic graphite coated nozzles, one subscale insert was re-fired successfully as an added task to the original program. This added task is described completely in the Addendum at the end of the report. Performance was completely normal and no cracking or delamination occurred. Pyrolytic graphite coated nozzles should be considered as good candidates for multiple firing cycle requirements.

TABLE OF CONTENTS

	Page
1.0 INTRODUCTION	1
2.0 SUMMARY AND CONCLUSIONS.	3
3.0 ANALYSIS AND DESIGN.	5
A. GENERAL.	5
B. THERMAL ANALYSIS	5
C. STRESS ANALYSIS.	14
1. Method of Analysis	15
2. Free Standing Pyrolytic Graphite Shells.	16
3. Coated Composites.	18
a. Coatings on Inner Surface of Cylinder.	19
b. Coatings on Outer Surface of Cylinder.	21
c. Effect of Substrate Properties	24
4.0 DEPOSITION STUDIES	29
A. GENERAL.	29
B. SUBSCALE INSERTS	29
C. FULLSCALE INSERTS.	32
D. CORRELATION OF RESIDUAL STRESSES AND OBSERVED CRACKS	38
5.0 MOTOR FIRING TESTS	43
A. TEST PROCEDURE	43
B. SUBSCALE MOTOR FIRINGS	43
1. Subscale Firing No. 1	50
2. Subscale Firing No. 2.	50
3. Subscale Firing No. 3.	55
4. Subscale Firing No. 4.	58

TABLE OF CONTENTS (CONT'D)

	Page
5. Subscale Firing No. 5.	58
6. Implication of Subscale Test Results	61
C. FULLSCALE MOTOR FIRINGS.	61
1. Fullscale Firing No. 1.. . . .	61
2. Fullscale Firing No. 2.. . . .	64
3. Fullscale Firing No. 3.	64
4. Fullscale Firing No. 4.. . . .	70
5. Implications of Fullscale Test Results	70
List of References.	74
APPENDIX A.	75
APPENDIX B.	93
APPENDIX C.	105
APPENDIX D.	133
APPENDIX E.	149
APPENDIX F.	177
ADDENDUM.	181

LIST OF FIGURES

<u>Figure</u>		<u>Page</u>
1	Effect of Pyrolytic Graphite Coating on Subscale Nozzle Temperatures.	9
2	Initial Temperature Rise in Pyrolytic Graphite Coating on Subscale Nozzle.	10
3	Temperature in Entrance Section of Subscale Nozzle.	11
4	Temperatures at Throat of Fullscale Nozzle.	12
5	Temperatures in Entrance Section of Fullscale Nozzle.	13
6	Pictorial Diagram Showing Parameters Related to Nozzle Slope.	22
7	Microstructure of Pyrolytic Graphite Coating on Insert for Subscale Firing Number 1.	31
8	Microstructure of Pyrolytic Graphite Coating at Entrance of Insert for Subscale Firing Number 3 (X150)	33
9	Microstructure of Pyrolytic Graphite Coating on Insert for Subscale Firing Number 4.	34
10	Microstructure of Pyrolytic Graphite Coating on Insert for for Fullscale Firing Number 1	36
11	Microstructure of Pyrolytic Graphite Coating on Insert for Fullscale Firings Number 2 and Number 3	37
12	Microstructure of Pyrolytic Graphite Coating on Insert for Fullscale Firing Number 4	39
13	Local Flaws Associated with Nodules in Coating on Insert for Fullscale Firing Number 4	40
14	Fullscale Test Motor During Firing.	46
15	Subscale Nozzle Assembly Drawing.	48
16	Components of Subscale Nozzle Prior to Assembly	49
17	Motor Pressure Traces for Subscale Firings No. 1 and No. 2. .	52
18	Axial View from Entrance End of Nozzle After Subscale Firing No. 1.	53

LIST OF FIGURES (CONT'D)

<u>Figure</u>		<u>Page</u>
19	Calculated Throat Radii During Subscale Firing No. 1.	54
20	Motor Pressure Traces for Subscale Firings No. 3 and No. 4. .	56
21	Microstructure of Pyrolytic Graphite Showing Evidence of Deformation After Subscale Firing Number 3.	57
22	Motor Pressure Trace for Subscale Firing No. 5.	59
23	Axial View from Entrance End of Nozzle After Subscale Firing Number 5	60
24	Fullscale Nozzle Assembly Drawing	62
25	Motor Pressure Traces for Fullscale Firings No.	63
26	Microstructure of Pyrolytic Graphite Coating After Fullscale Firing Number 2	65
27	Motor Pressure Traces for Fullscale Firings No. 3 and No. 4 .	66
28	Axial View from Entrance End of Nozzle After Fullscale Firing No. 3.	67
29	Oblique View from Entrance End of Nozzle After Fullscale Firing No. 3.	68
30	Microstructure of Pyrolytic Graphite Coating.	69
31	Axial View from Entrance End of Nozzle After Fullscale Firing No. 4.	71
32	Axial View from Exit End of Nozzle After Fullscale Firing No. 4.	72
33	Microstructure of Pyrolytic Graphite Coating After Fullscale Firing No. 4.	73

LIST OF TABLES

<u>Table</u>		<u>Page</u>
I.	Dimensions of Nozzles Selected for Thermal Analysis	7
II.	Summary of Residual Stresses in As-Deposited Free-Standing Cylinders of Pyrolytic Graphite	17
III.	Summary of Residual Stresses in Cylindrical Composites with Pyrolytic Graphite Coatings on the Inside	20
IV.	Summary of Residual Stresses in Cylindrical Composite with As-Deposited Pyrolytic Graphite Coatings on the Outside . . .	23
V.	Effect of Substrate Properties on Stresses in Composite Cylinders	25
VI.	Correlation of Calculated Stresses and Observed Delamination Cracks.	41

1.0 INTRODUCTION

Pyrolytic graphite is a unique form of graphite produced by vapor deposition of carbon from a carbonaceous source gas on a heated substrate. It exhibits excellent erosion resistance when used in uncooled nozzles for solid propellant rocket motors. Its high density, essentially zero permeability, and complete absence of a binder phase are believed to explain this exceptional serviceability. Subscale rocket motor tests of pyrolytic graphite coated nozzles of 1/2-inch throat diameter carried out previously at Atlantic Research Corporation have shown that consistently good performance can be achieved in nozzle service with propellants having flame temperatures from 5600 F to 6550 F. (Ref. 1) The higher the flame temperature and the motor operating pressure, the higher the erosion rate observed for pyrolytic graphite. To illustrate the high erosion resistance of pyrolytic graphite coatings, 1/2-inch diameter nozzles fired with 6550 F propellant have shown average erosion rates of the order of 0.5 mil/sec at 700 psi motor pressure. Limited tests with 1-inch diameter nozzles with a 6000 F propellant have also shown low erosion rates but the problems of scale-up have not been previously investigated sufficiently.

The lowest chemical reactivity can be achieved by using pyrolytic graphite as a coating so that the layer plane surfaces are exposed to the propellant combustion gas environment. However, to use the coating orientation, the difficulties and problems involved in maintaining coating integrity, which are common to all coating systems, must be accepted and solved. The anisotropic properties of pyrolytic graphite make the problem of maintaining coating integrity more severe than usual. Residual stresses are unavoidably built into the coating during the deposition process. The exposure of a pyrolytic graphite coating to the thermal shock conditions of nozzle service may also lead to coating compromise.

To circumvent the problems of maintaining coating integrity, many nozzle designers have resorted to the use of edge-oriented pyrolytic graphite in the form of stacked discs or washers. However, depending upon the heat sink capacity of the nozzle design and the severity of the service conditions, it has been found that edge-oriented pyrolytic graphite erodes up to several times faster than a good coating of pyrolytic graphite. A pyrolytic graphite coating is a good thermal insulator and coated nozzle inserts do not depend upon heat sink capacity to perform satisfactorily. Thus, a pyrolytic graphite coated nozzle can be designed for minimum volume and minimum weight. The potential exists, therefore, using pyrolytic graphite coatings, to prepare a nozzle of superior performance capabilities as well as minimum weight.

Previous work has been carried out to evaluate pyrolytic graphite coatings made by several suppliers (e.g., Ref. 2 and 3), but no definitive and systematic study of the feasibility of pyrolytic graphite coated nozzles of reasonable size and for severe motor operating conditions has been reported. Such a feasibility demonstration was the principal objective of this program.

To investigate the feasibility and the performance capabilities of pyrolytic graphite coated nozzles for solid propellant rocket motors operating under severe conditions, the current program consisted of the detailed analysis, fabrication and motor testing of a group of nozzles with an advanced propellant of 6550° F flame temperature. Five subscale nozzles of 1.1-inch nominal throat diameter for an 1100-lb thrust motor and four fullscale nozzles of 2.3-inch nominal throat diameter for a 4600-lb thrust motor were fabricated and motor tested. The preparation of the coated nozzle inserts, the fabrication of the test nozzles, and the rocket motor test of these units were all carried out at the facilities of the Atlantic Research Corporation. This report describes in detail the work carried out and the results achieved in this program.

2.0 SUMMARY AND CONCLUSIONS

The principal objective of this program was to demonstrate the feasibility of pyrolytic graphite coatings for uncooled nozzle service under severe operating conditions. Based on prior work in the field, it was apparent that a pyrolytic graphite coating represented a highly erosion resistant nozzle material. The utilization of this material, however, required a demonstration that coatings of suitable quality and integrity could be prepared and could perform successfully in rocket motor firings.

To accomplish this objective, both thermal and stress analyses were completed to aid in the design of the test nozzles and to aid in the understanding of their behavior during tests. Deposition studies were carried out to demonstrate that suitably coated inserts could be prepared for fabrication of test units for the motor firing program. Rocket motor tests of both subscale and fullscale nozzles were performed using a 6550 F flame temperature propellant at a nominal motor pressure of 700 psi. The motor firing program culminated in a demonstration of the ability of pyrolytic graphite coatings to withstand firings in excess of 60 seconds at high chamber pressure.

A number of interesting conclusions can be drawn from this program. The thermal analyses illustrated the unique insulating properties of pyrolytic graphite coating and provided design data for the successful fabrication and test of the nozzles built on this program. The stress analyses provided data on the residual stresses in composite bodies consisting of a pyrolytic graphite coating and the substrate upon which it was deposited. These data were not previously available in the literature. The effect of pyrolytic graphite coating thickness, substrate thickness, substrate radius, and substrate properties were illustrated by stress calculations. Based upon the stress calculations and the experimental evidence gathered in the deposition work, it was concluded that both the radial tensile stress in the pyrolytic graphite coating and the axial stress in the substrate material are critical in causing flaws in the coating.

In the deposition studies, it was determined that delamination cracking is the most common failure mode from residual stresses in pyrolytic graphite coated composites. For a given substrate material, delamination cracking occurred at similar coating thicknesses for both the subscale nozzles (1.1-inch diameter) and fullscale nozzles (2.3-inch diameter). This behavior indicates that critical stress factors may result both from the anisotropic nature of the pyrolytic graphite and from mismatch between the coating properties and the substrate properties. Control of delamination cracking was achieved both through deposition process control and through selection of the substrate material. Crack-free coatings of about 50 mil thickness were successfully prepared on conventional graphite substrates of both subscale and fullscale dimensions. Much thicker crack-free coatings were prepared on a low modulus, fibrous graphite substrate. Correlation of the calculated stress levels and the experimentally observed cracking was achieved.

CONFIDENTIAL

AFRPL-TR-65-57

Nine motor firing tests (five subscale nozzles and four full scale nozzles) were made with a 6550⁰F propellant at 700 psi motor pressure. Excellent performance was demonstrated for both subscale nozzles (erosion rates from 0.55 to 0.64 mil/sec) and fullscale nozzles (erosion rates from 0.73 to 1.19 mil/sec). The higher erosion rates were measured for coatings on fibrous graphite substrates probably because of a greater tendency to form nodules in these coatings and the local flaws associated with nodules. The extent of coating deterioration and loss correlated with observed pre-firing delamination cracks. Three coatings which contained known delamination flaws (two subscale and one fullscale insert) prior to firing were all destroyed during motor test. Of six coated inserts without observable major flaws, only one subscale unit suffered a complete loss of coating. Coating retention was demonstrated in the other five tests of inserts without cracks; four of these successful tests were consecutive in the latter portion of the program. Calculated stress values for both radial coating stress and axial substrate stress were correlated with the observed delamination cracks. The value of the pre-firing microscopic examination of the coating edges as a quality control procedure was clearly demonstrated by the program results. (C)

Post-firing microscopic examination of the coating on several inserts showed no deterioration of the remaining coating. This indicates that pyrolytic graphite coatings are a good candidate for restart nozzle applications. (U)

The feasibility of pyrolytic graphite coatings for use in uncooled nozzles for advanced solid propellant motors was demonstrated by the results of this program, but several areas are recommended for further study to optimize the coating performance and to advance the development of such nozzle assemblies. Stress analysis work should be extended to confirm the critical allowable stresses in coated composites and to optimize the control of these critical stresses. Deposition work should be aimed at the preparation of optimum quality coatings and the correlation of erosion resistance with microstructure. Repetitive motor firings of coated nozzles is recommended to demonstrate the indicated utility of pyrolytic graphite coatings for this type of duty cycle. Additional motor tests could provide experimental data for the correlations sought in further stress analysis and deposition process study. (U)

CONFIDENTIAL

3.0 ANALYSIS AND DESIGN

A. GENERAL

It is important in the evaluation of nozzle materials that the proper design be used for each test unit. When the objective is to evaluate the performance capability of the nozzle material, any short-coming of the design which compromises this performance is misleading and undesirable. To aid in the design of the test nozzles, both thermal analysis and stress calculations were carried out. Thermal analysis was carried out to determine the temperature history of the nozzle structure and to assure that thermal failures would not occur. The stress calculations carried out dealt with the residual stresses involved in the pyrolytic graphite coated insert. All of the test nozzles were constructed with heavy-weight test hardware to provide the maximum data on the nozzle inserts within the limited budget of the program. Design and optimization of a flight-weight nozzle were beyond the scope of this program.

Both the thermal analysis and the stress analysis calculations are discussed in some detail in this section because the results of these calculations indicate some of the unique properties of pyrolytic graphite coated nozzles. The thermal analysis indicates the potential for minimum weight nozzles offered by pyrolytic graphite coatings. The stress analysis indicates the nature of the problems faced in preparing flaw-free coatings of desired dimension and in maintaining coating integrity during service.

B. THERMAL ANALYSIS

Pyrolytic graphite is an excellent thermal insulator in the direction normal to the deposition layer planes. When used as a coating this insulating property leads to a rapid rise in surface temperature, large temperature gradients across the coating thickness, and a significant reduction in the heat transmitted through the coating to the nozzle structure. The high surface temperature and large thermal gradients across the coating produce very severe service conditions for the pyrolytic graphite, but, if the coating can withstand these conditions, the reduction in heat transmission through the coating makes possible a very light-weight nozzle system. This characteristic is a distinct advantage for pyrolytic graphite coatings over conventional heat sink nozzles.

To predict the temperature history at several points in selected nozzle designs, a series of thermal analyses was carried out. Several cases were selected to provide a parametric study of the effect of coating thickness, substrate thickness, and insulating thickness for both the subscale and full-scale nozzles. The thermal analyses were performed with existing programs on a Burroughs 220 and an IBM 7090 computer. These programs utilize finite difference methods to calculate the transient radial conduction in axisymmetric cylindrical geometry and include the following features:

(1) Convective heat input at the gas surface is based on Bartz correlation transfer coefficients and gas recovery temperature.

(2) Radiative heat transfer at the gas surface is based on the particle cloud and surface emissivities and the gas free-stream temperature (i.e., no temperature lag in the condensed phase).

(3) Temperature dependent thermal properties are used as needed for each material in the composite structure.

(4) An adiabatic rear wall condition is assumed. Factors 1 and 4 are conventional assumptions generally made in all thermal analysis programs. The refinements of the program used in this study are the inclusion of temperature dependent thermal properties and the inclusion of radiative heat transfer between the nozzle surface and the propellant exhaust stream. The latter factor is quite important for long term firings when the surface temperature of the nozzle approaches a steady state value. If radiative heat transfer is ignored, significant error may exist in the calculated surface temperature. The use of a program for axisymmetric cylindrical geometry is also extremely desirable for nozzles of moderate diameter.

Calculations of the temperature histories were made for both subscale and fullscale nozzles at the nozzle throat location and at one upstream position in the nozzle inlet region. At the throat location, the composite structure consisted of pyrolytic graphite coating, graphite substrate, carbon back-up insulation, and steel structure. An edge-oriented pyrolytic graphite plate was used just upstream of the coated insert in the experimental nozzles to protect the leading edge of the coated section. Thus, the thermal analyses in the inlet region were made for a composite consisting of edge-oriented pyrolytic graphite, a baked carbon insulator, and the steel structure. In all calculations ATJ graphite was taken as the substrate material and baked carbon, which was used in all of the test nozzles, was taken as the insulation and back-up material. In each case, a standard thickness of 3/8 inch was used for the steel nozzle structure.

A total of fifteen cases were analyzed. The dimensions of each configuration selected for analysis are shown in Table I. The dimensions used for thermal analyses covered a range of dimensions anticipated to cover those used in actual experimental nozzle designs. The data calculated for each case are summarized in tabular form in Appendix A. The reader may refer to these data for any detailed comparisons desired. Selected data are discussed and compared in the following paragraphs to illustrate key features of pyrolytic graphite coated nozzles.

Several interesting facts may be noted by examining the predicted temperature histories. First, the very strong effect of the insulating nature of the pyrolytic graphite coating is apparent from the rate at which heating of the nozzle occurs at the throat region compared to a nozzle without the

Table I. Dimensions of Nozzles Selected for Thermal Analysis.

A. Throat location: 1.100" throat diameter; 4.750" outside diameter; steel thickness 3/8"

<u>Case No.^a</u>	<u>Pyrolytic Graphite Coating Thickness (mil)</u>	<u>Graphite Thickness (inch)</u>	<u>Graphite/Carbon Interface Diameter (inch)</u>	<u>Carbon Thickness (inch)</u>
A-1	0	0.700	2.500	0.75
A-2	0	0.950	3.000	0.50
A-3	30	0.670	2.500	0.75
A-4	30	0.920	3.000	0.50
A-5	60	0.640	2.500	0.75
A-6	60	0.890	3.000	0.50

B. Throat location: 2.300" throat diameter; 6.250" outside diameter; steel thickness 3/8"

<u>Case No.</u>	<u>Pyrolytic Graphite Coating Thickness (mil)</u>	<u>Graphite Thickness (inch)</u>	<u>Graphite/Carbon Interface Diameter (inch)</u>	<u>Carbon Thickness (inch)</u>
B-1	0	0.850	4.000	0.75
B-2	0	1.100	4.500	0.50
B-3	45	0.805	4.000	0.75
B-4	45	1.055	4.500	0.50
B-7	45	0.805	4.000	1.125 ^b

C. Inlet location: 1.840" diameter (1.100" throat); steel thickness 3/8"

<u>Case No.</u>	<u>Pyrolytic Graphite Plate Web Thickness (inch)</u>	<u>Carbon Thickness (inch)</u>	<u>Outside Diameter (inch)</u>
C-1	0.830	0.50	5.250
C-2	0.830	0.875	6.000

D. Inlet Location: 3.540" diameter (2.300" throat); steel thickness 3/8"

<u>Case No.</u>	<u>Pyrolytic Graphite Plate Web Thickness (inch)</u>	<u>Carbon Thickness (inch)</u>	<u>Outside Diameter (inch)</u>
D-1	0.855	0.625	7.250
D-2	0.855	1.000	8.000

a. Results of these cases are found in Appendix A.

b. Outside diameter for case B-7 = 7.000"

pyrolytic graphite coating. (Figure 1) This insulating property of the coating leads to the predicted very rapid rise in surface temperature. Just how rapidly this rise occurs can be seen in Figure 2 in which the surface temperature of the throat of a subscale nozzle with only 30 mils of pyrolytic graphite coating is shown with a greatly expanded time scale. It can also be seen from these temperature plots that practical thicknesses of baked carbon in the range from 1/2 to 1 inch provide adequate insulation between the nozzle throat insert and the steel housing for all the firing conditions planned in this program (Figures 1 and 4).

The temperature histories predicted in the inlet region of both the subscale nozzle and the fullscale nozzle are shown in Figures 3 and 5. A substantial temperature rise can be expected from the heat sink, edge-oriented pyrolytic graphite plate, but this need be no cause for concern for heavy-weight nozzle test hardware. The edge-oriented pyrolytic graphite plate is included for the primary purpose of providing protection for the leading edge of the coated insert section. In previous work, excessive erosion upstream of the coated insert has led to unduly severe exposure conditions of the coating. In practical nozzle designs, no greater weight of the pyrolytic graphite plate material would be desirable beyond that needed to provide protection for the upstream edge of the coating. To optimize a light-weight nozzle design, another method of controlling the entrance contour, such as the use of a second pyrolytic graphite coated segment, might be found more favorable.

The dimensions of the nozzles which were motor tested were comparable with cases subjected to thermal analysis. The thermal calculations indicated that no problems would be encountered with over heating of the nozzle structures. These predictions were borne out in the motor test firing program.

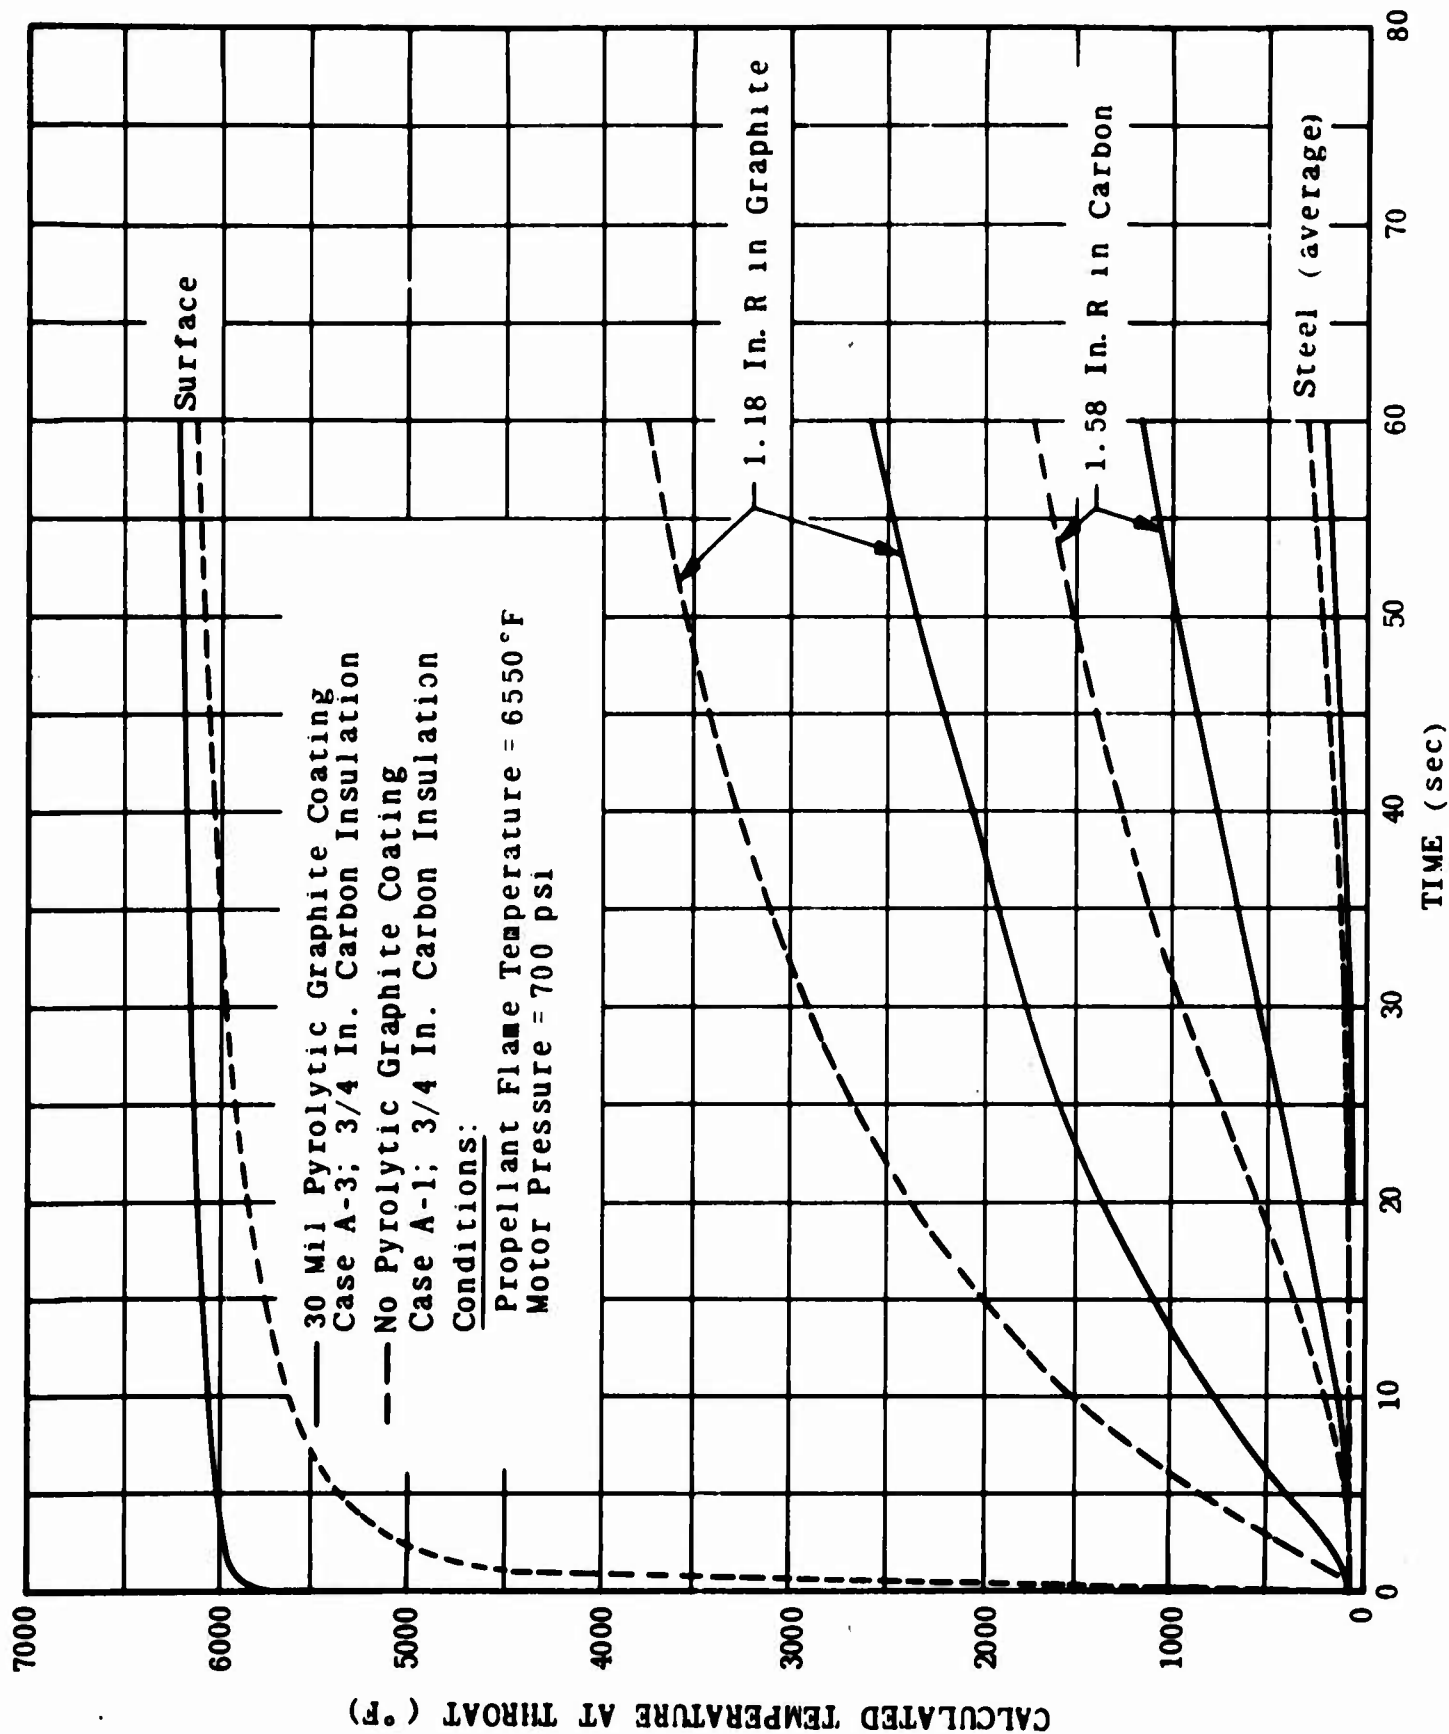


Figure 1. Effect of Pyrolytic Graphite Coating on Subscale Nozzle Temperatures.

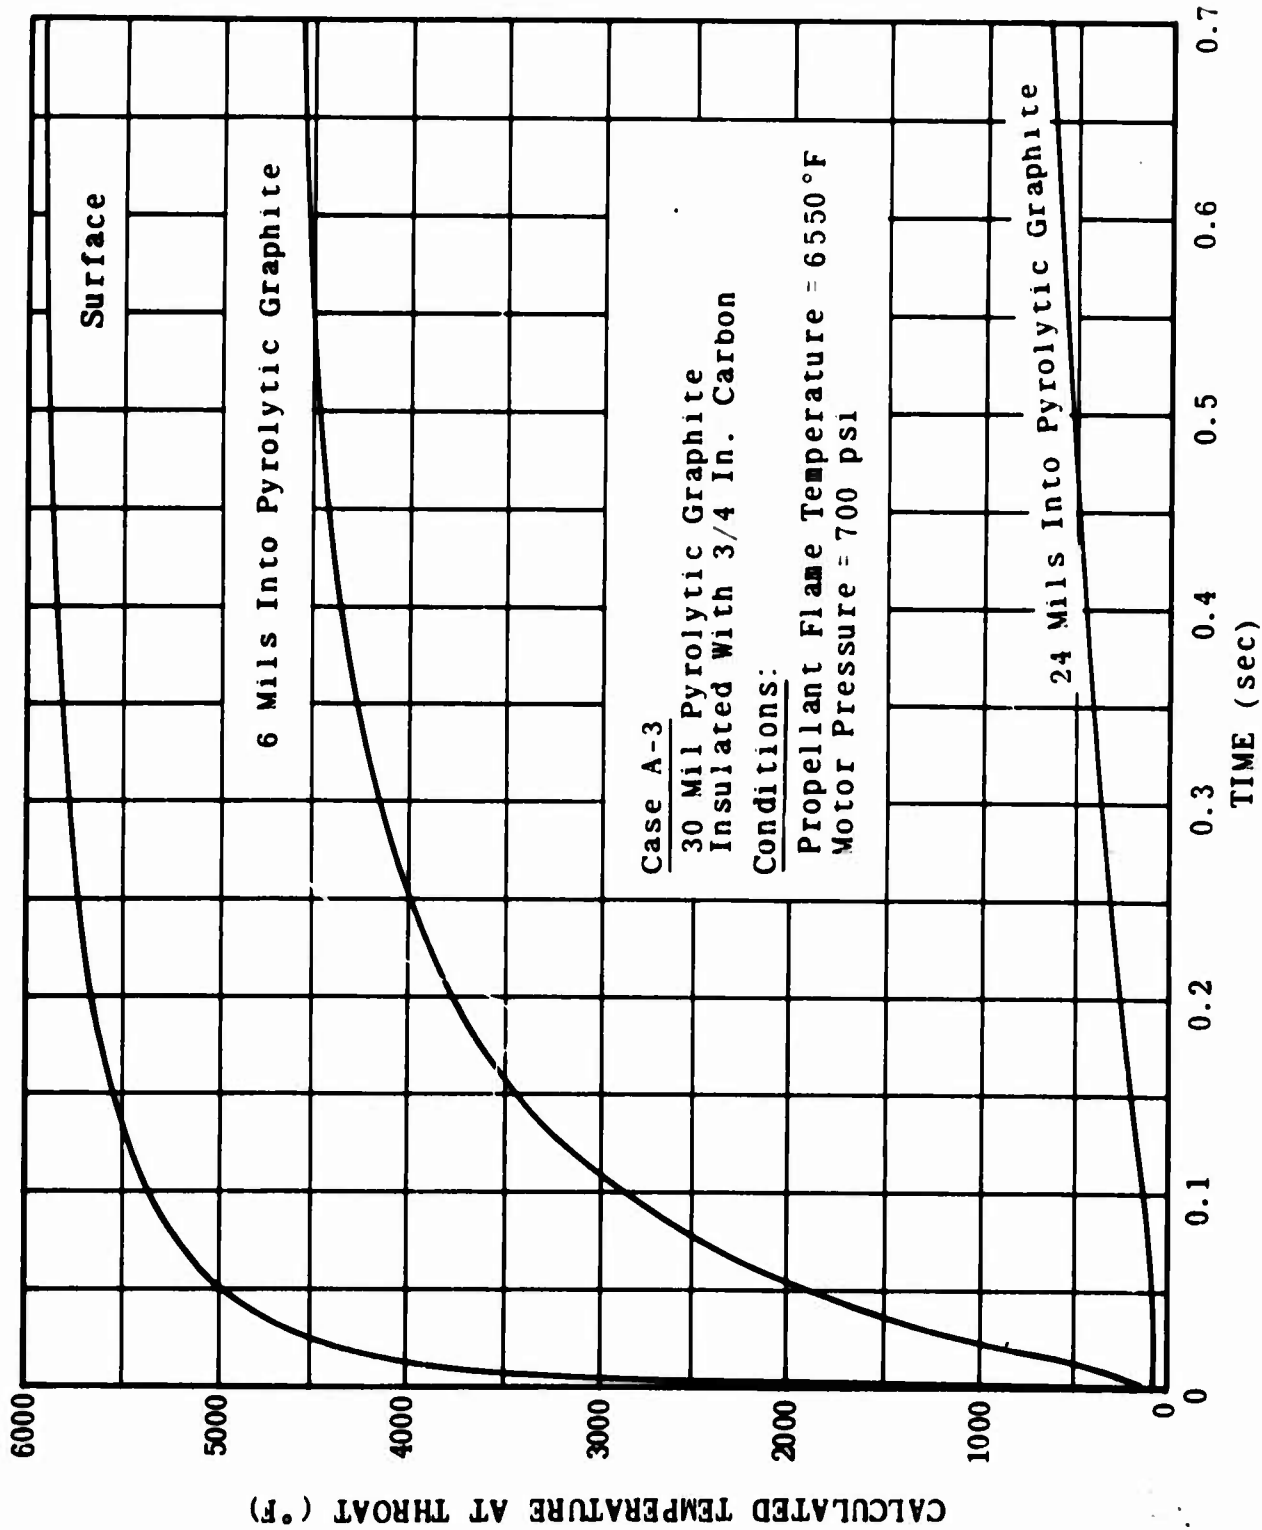


Figure 2. Initial Temperature Rise in Pyrolytic Graphite Coating on Subscale Nozzle.

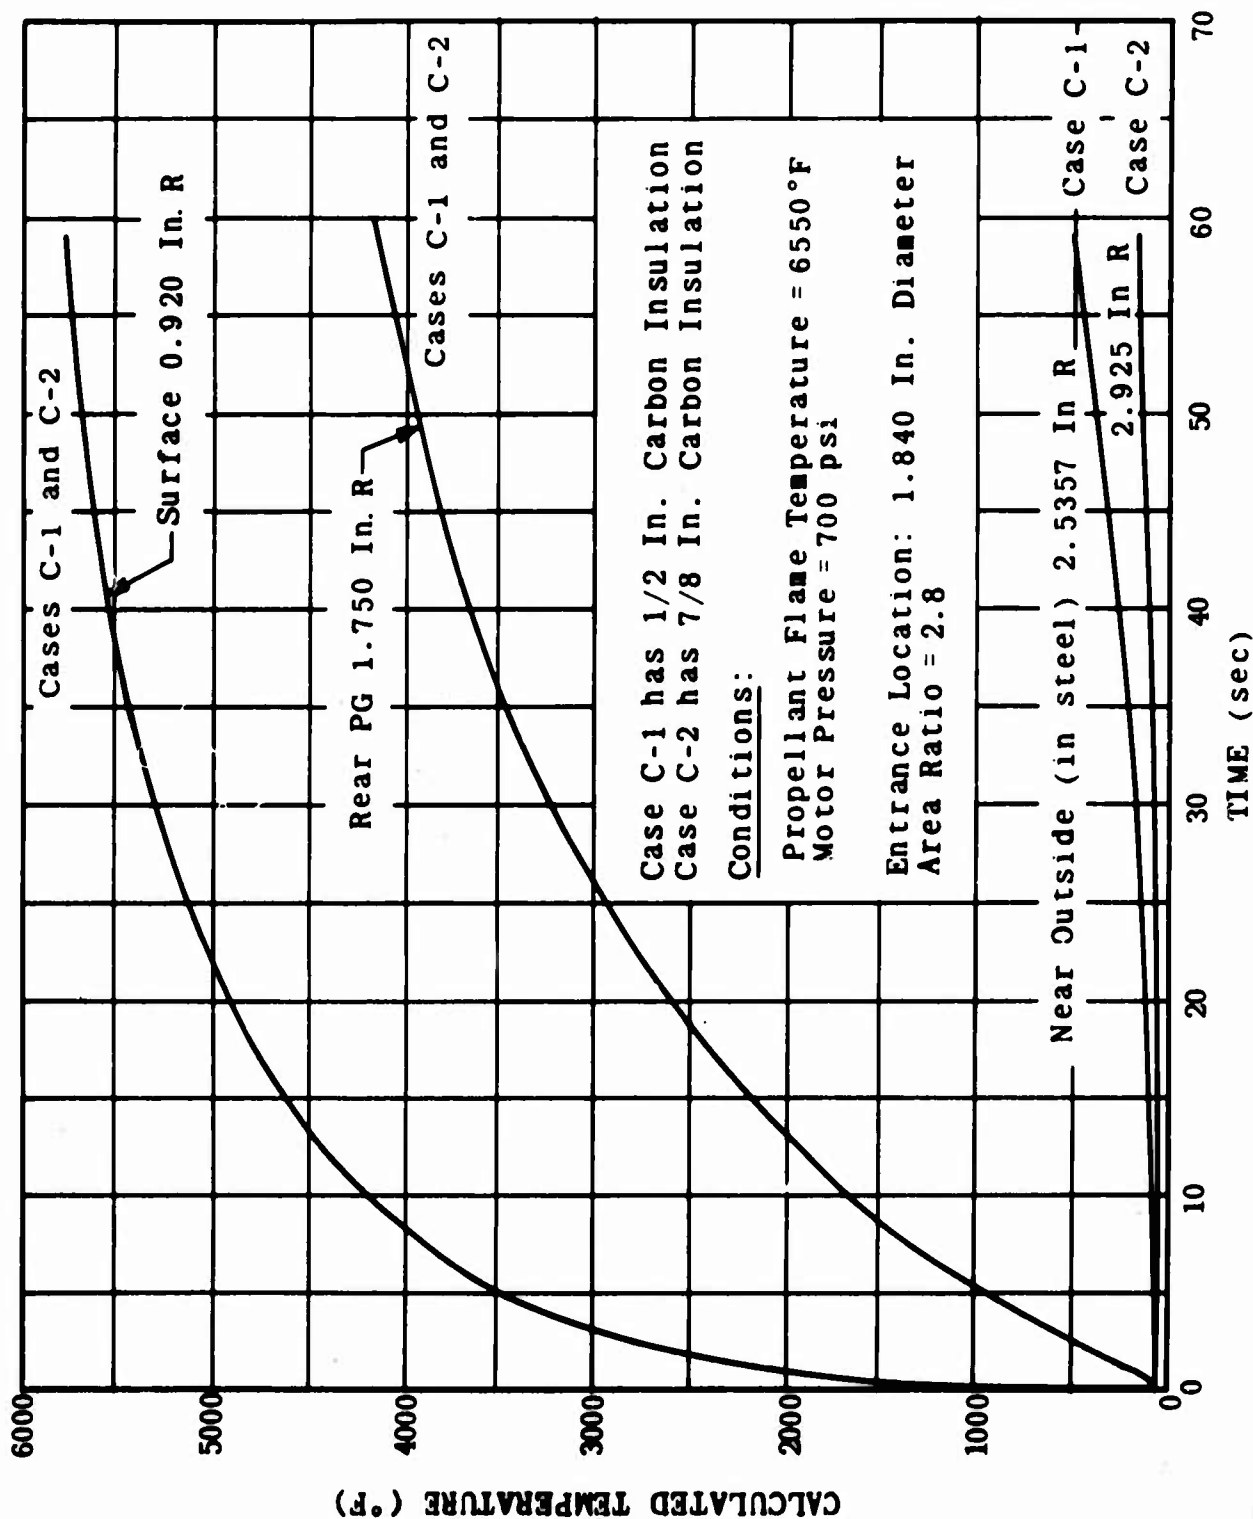


Figure 3. Temperature in Entrance Section of Subscale Nozzle.

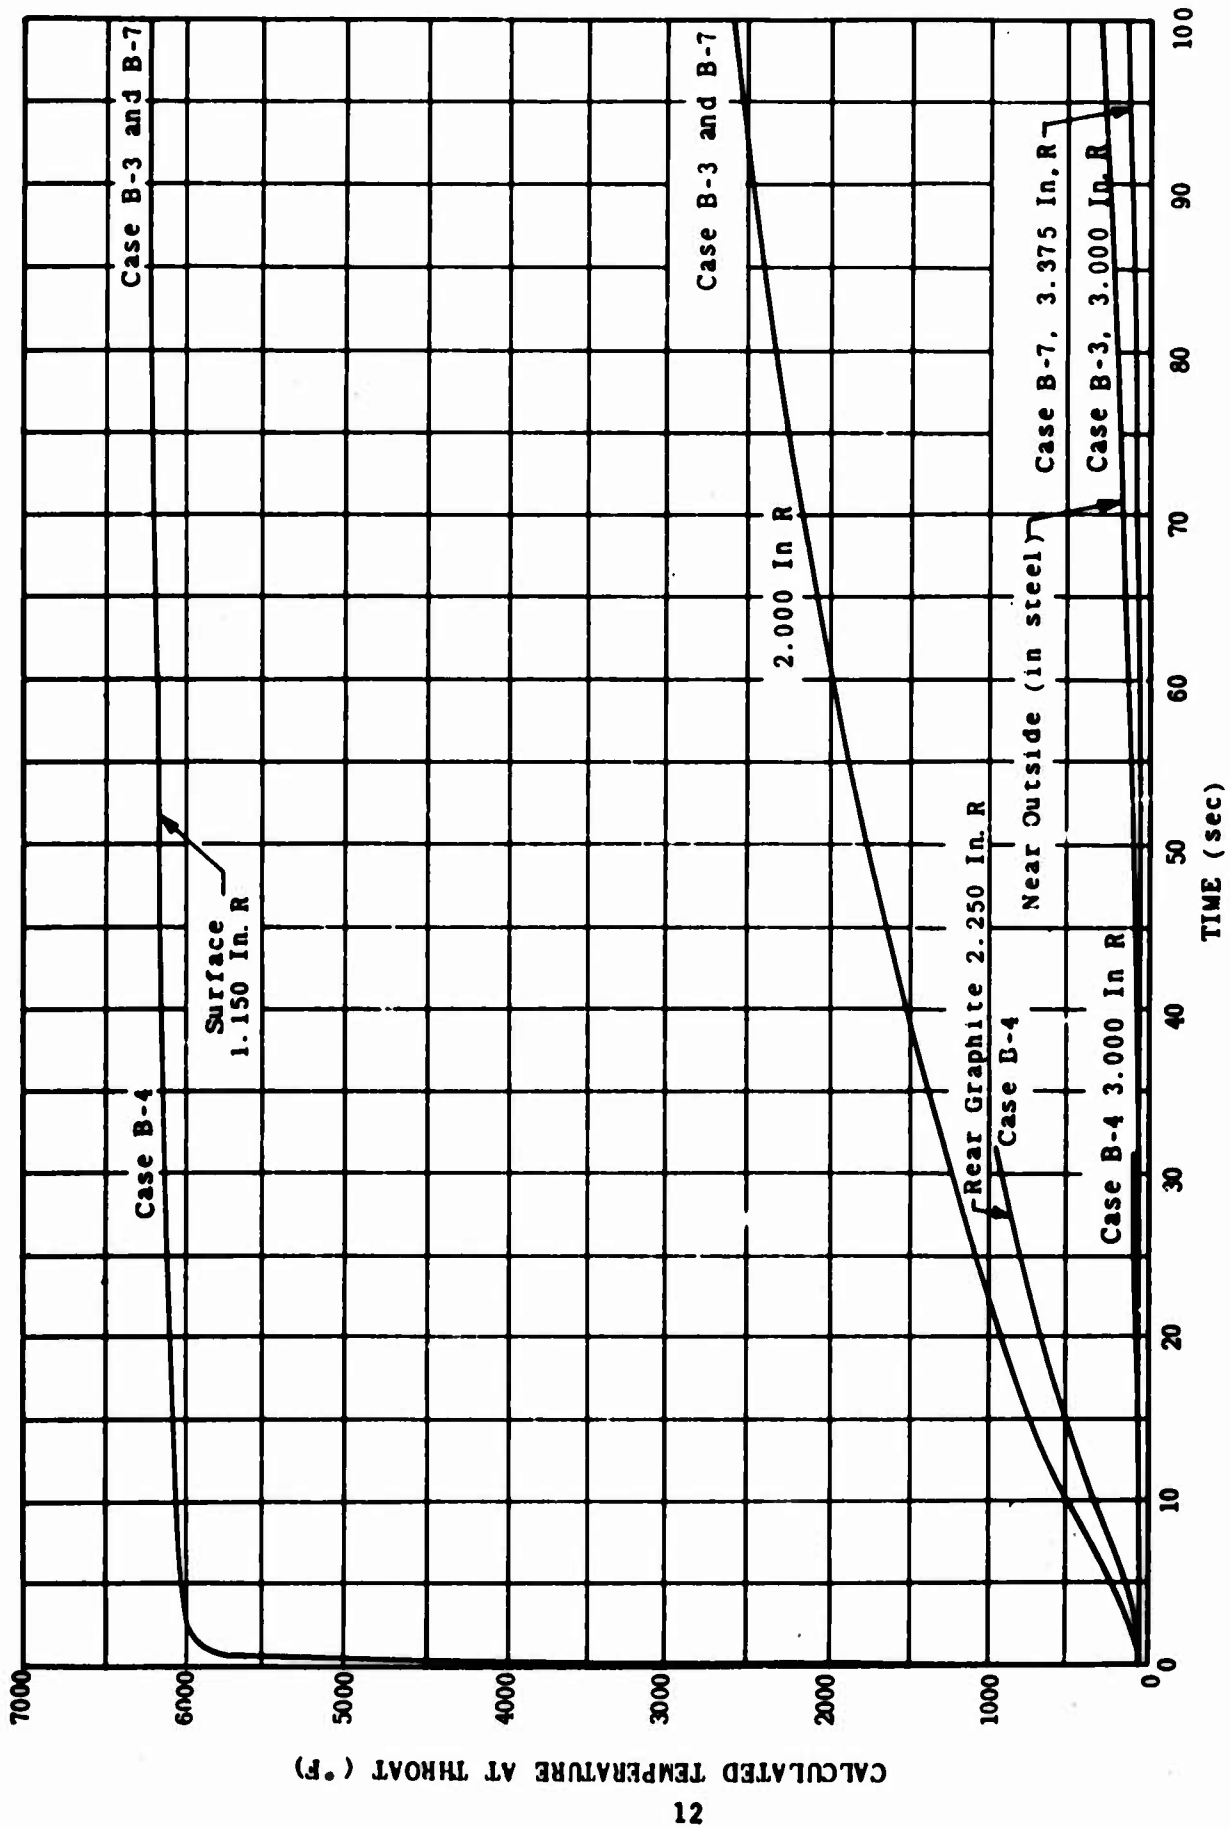


Figure 4. Temperatures at Throat of Fullscale Nozzle.

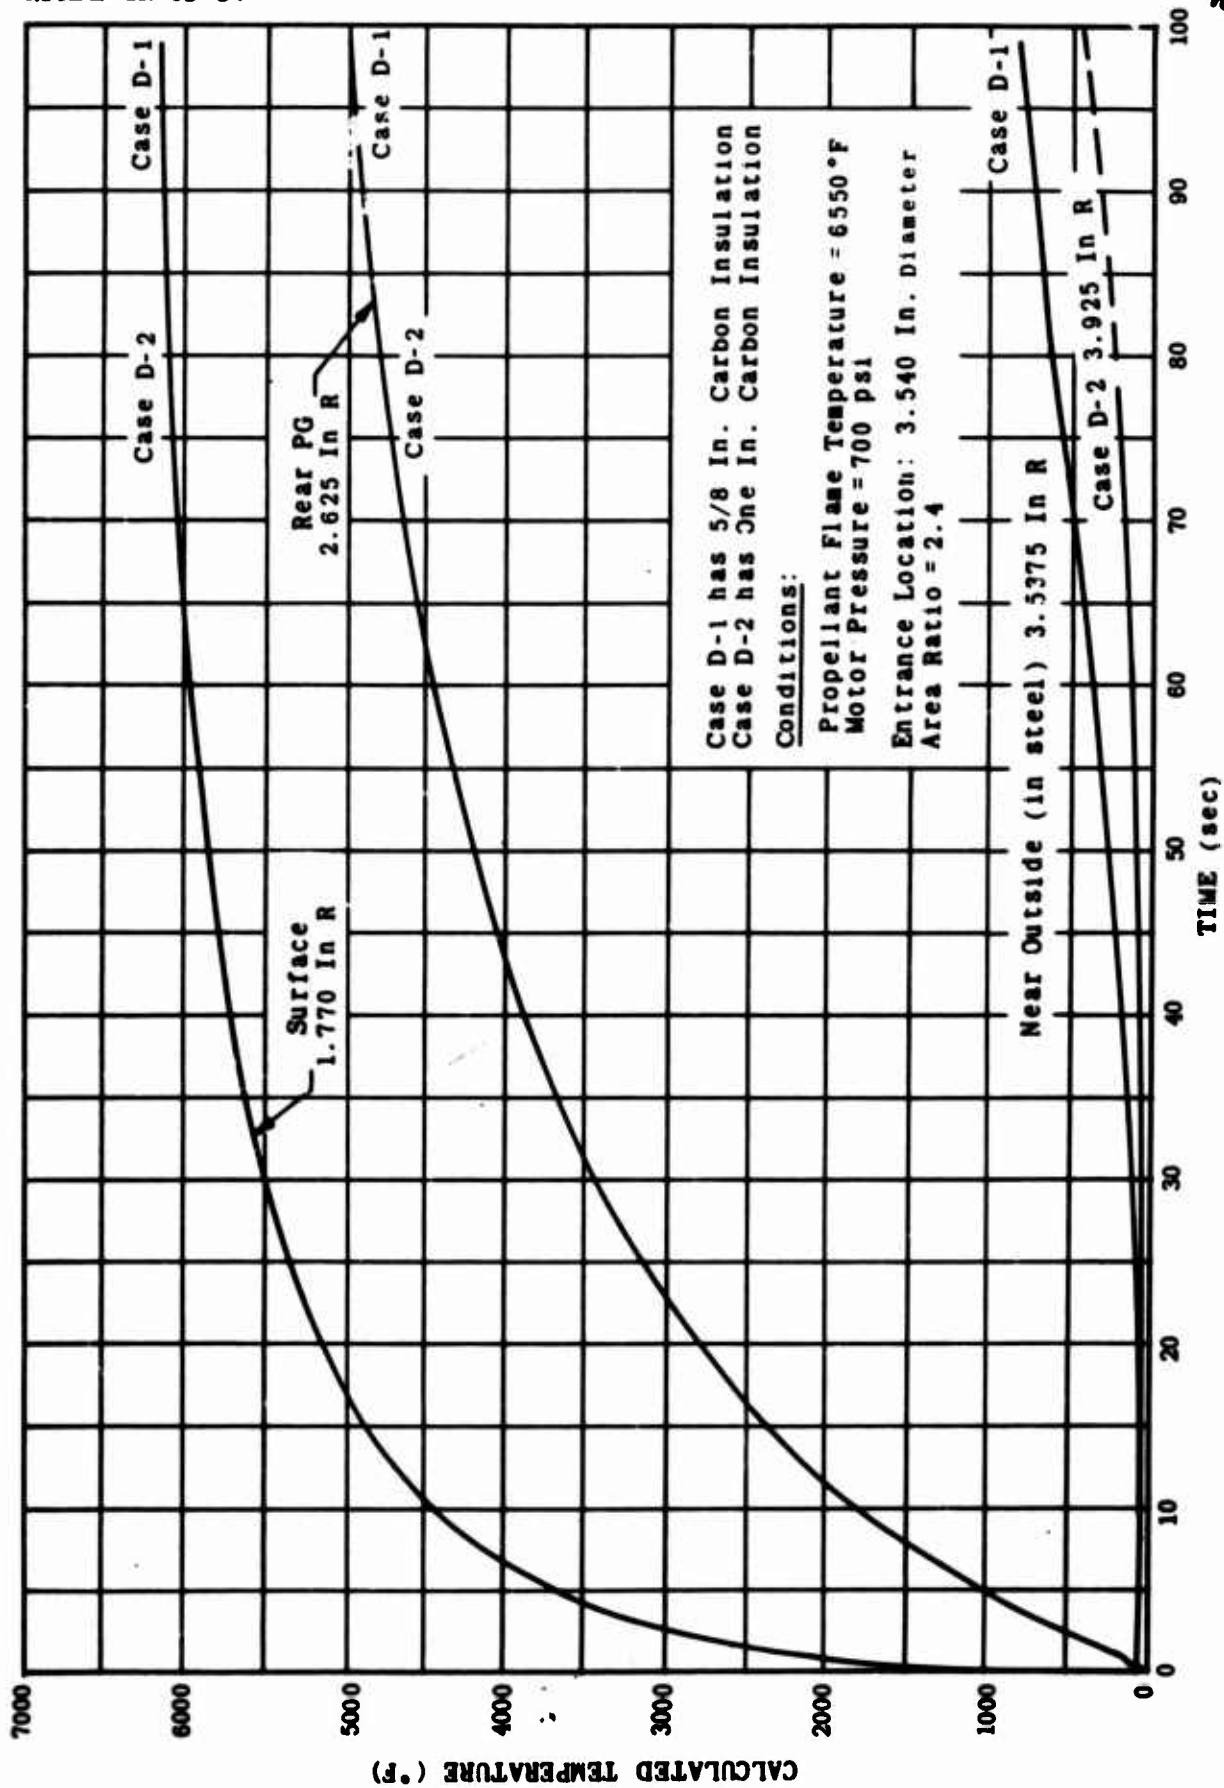


Figure 5. Temperatures in Entrance Section of Fullscale Nozzle.

C. STRESS ANALYSIS

In the design of any nozzle, various stress factors must be considered. Stresses exist in the throat insert, in the back-up insulation, and in the nozzle structure. In a flight-weight nozzle design, the stress levels in the nozzle structure and attachments assume equal importance with the stresses in the internal components of the nozzle. This is true because each component must be designed to save weight. When heavy-weight nozzles are designed for test purposes, however, the structural stress problems may be minimized by conservative design. The conservative design for the test hardware used on this program contributed to the satisfactory performance experienced with the test nozzles to yield maximum data on the coating performance.

Stress factors in the nozzle throat insert material under evaluation cannot be disposed of easily. These stress factors and their effect upon the nozzle material are often central to the performance capabilities of the material. Residual stresses may be incorporated in the nozzle insert material during its manufacture. Additional stresses or modification of the residual stress pattern may be caused during a rocket firing both by the severe thermal environment and the mechanical forces acting upon the nozzle. Often one of these stress types is critical for the application of a given nozzle material. Such was the case in this program as indicated in the following discussion.

Pyrolytic graphite is a highly anisotropic material. Because the material consists of a stacked layer plane structure, the thermal and mechanical properties are very different in the a-b direction (parallel to basal planes) in the c- direction (perpendicular to the basal planes). The elastic constants of the material also differ in the a-b and c directions. A material which exhibits this type of anisotropy, in which the properties in two directions (a-b) are equivalent but differ from those in the third direction (c), is properly referred to as transversely isotropic. It is known that a transversely isotropic material is prone to develop residual stresses when its temperature is changed. A change in the temperature of the material is a sufficient condition to induce stresses; it is not necessary for a temperature gradient to exist in the material as is the case for an isotropic material. In the case of a flat piece of pyrolytic graphite, the stresses induced during cooling from the deposition temperature lead to warping or distortion of the surface. However, in closed shells of pyrolytic graphite, the geometrical restraint offered by the closed shape locks in residual stresses.

The residual stresses inherent in pyrolytic graphite coatings represent the single most critical stress factor in pyrolytic graphite nozzles. Although the general nature of the residual stresses in pyrolytic graphite are known, little definitive information has been published on the magnitude of these stresses especially for the composite consisting of a pyrolytic coating and its graphite substrate. An approximate analysis of the stresses in free-standing spherical and cylindrical shells of pyrolytic

graphite was reported in Reference 4. In both references 4 and 5, the local effects of nodules and surface roughness were explored for free-standing geometry. Reference 6 contains, in addition to the work published in References 4 and 5, a variety of brief and exploratory analyses of many of the different stress problems such as growth, thermal gradients, surface roughness, etc., discovered in the course of the fabrication of pyrolytic graphite shapes. Calculations are made only for free-standing shells although the effects of mandrel restraints are suggested. Perhaps most important in Reference 6 is the exploration of methods of measuring residual stresses by strain gage techniques. It appears that with sufficient care and extensive effort residual stresses can be measured, but such measurements require destruction of the pyrolytic graphite section. The data in the literature is of general interest, but it does not relate the stresses in coated composite structures to the geometry and properties in the way required to guide a study of pyrolytic graphite coated nozzles.

The principal mode of failure of coated inserts resulting from residual stress consists of delamination cracks which are parallel to the substrate and coating free surface. Such cracks may form at the substrate coating interface or completely within the coating and once initiated generally propagate around the nozzle circumference. Radial tensile stresses in the coating are normal to such cracks and could be responsible for delamination. Shear stresses resulting from axial stresses in short coated pieces could also produce interlaminar failure. The axial curvature of the nozzle would lead to an opening of an interlaminar crack following a shear stress failure. Microscopic examination of the polished edge of the coating readily reveals delamination cracks; the prediction and control of such flaws was the main objective of the stress analyses. Short interlaminar cracks are often found in the region of growth nodules in local areas of otherwise sound coatings. These defects, which are referred to as local flaws because they do not form a continuous crack pattern, would likely be less destructive coating integrity.

To define the problems inherent in the as-deposited coatings under study in this program, a series of stress analyses was carried out. Calculations were made on the effect of geometrical variables on the residual stress in free-standing pyrolytic graphite shells. Calculations were also made for the effect of geometry and substrate properties on the stresses in composites consisting of a pyrolytic graphite coating and its substrate. The method used in these calculations and the results of each type of calculation are discussed in the following sections.

1. Method of Analysis

In a previous program at Atlantic Research (Reference 1), the basic stress-strain relations for pyrolytic graphite were derived. These relationships for a transversely isotropic material are much more complicated than for the case of an isotropic material. The stress-strain relationships involve seven elastic constants rather than three for an isotropic case. However, only five of these elastic constants are independent.

In our prior work, these stress-strain relationships were used to derive the differential equations relating the stresses and the deflections for a cylinder of pyrolytic graphite. These equations were the starting point for the calculations of stresses in pyrolytic graphite shapes which can be described in cylindrical coordinates.

To carry out the desired stress analyses on this program, computer programs were written to solve the basic equations on a Burroughs 220 computer. The first program prepared dealt with the stresses in a homogeneous free-standing cylinder of pyrolytic graphite. This program was used to calculate the stresses in long cylinders in which the edge effects were not involved. The input data required for this program were the thermal and elastic properties of the pyrolytic graphite and the temperature at which the material was in a stress-free condition. The output of the program consisted of the principal stresses at any other temperature.

A second computer program was also prepared in which the pyrolytic graphite coating equations were coupled with those which apply to a cylindrical substrate material. This program could be used to calculate the stresses in both the coating and the substrate for composites in which the coating is on either the inside or the outside of the substrate cylinder. This program was particularly important to our study of pyrolytic graphite coated inserts. The interaction of the coating and the substrate cannot be ignored if pyrolytic graphite is to be used on an as-deposited coating basis. No serious study of the stresses in as-deposited composites was available from previous work so that this portion of our stress analysis was critical in the guiding of our deposition studies and the interpretation of the results of this deposition work.

2. Free Standing Pyrolytic Graphite Shells

As indicated above, the anisotropic nature of pyrolytic graphite leads to residual stresses in any shell when the temperature of the material is changed. Although these stresses cannot be eliminated or avoided, an identification of the nature and magnitude of these residual stresses is of value in the design of a nozzle.

The stresses in long cylinders of free-standing pyrolytic graphite were calculated using anisotropic elastic and thermal expansion properties for the pyrolytic graphite. The stresses considered in each case are those created by cooling the material, assumed stress free at the deposition temperature of 2000°C, to room temperature. The thickness of the pyrolytic graphite shell and its diameter were varied over a range typical of those values of interest for the nozzles in this program. The maximum tensile stresses calculated in each of the eight cases considered are listed in Table II. A complete description of the stresses calculated and the input data used in this series of calculations are contained in Appendix B. Compressive stresses are not listed in Table II since failures caused by such stresses are rarely observed and were certainly not involved in the cracking found experimentally in this program. It must be remembered that the stresses calculated for free-standing pyrolytic graphite shells are

Table II. Summary of Residual Stresses in As-Deposited Free-Standing Cylinders of Pyrolytic Graphite.

Case No. ^a	Inside Dia. (inch)	Coating Thickness (mil)	t/r_1^b	Max. Tensile Stresses		
				Radial ^c (psi)	Hoop ^d (psi)	Axial ^e (psi)
1	1.120	30	0.0536	66	5,120.	744.
2	1.120	50	0.0894	176	8,470	1,166
3	1.120	80	0.143	427	13,400	1,660
4	2.300	30	0.0261	16	2,500	832
5	2.300	50	0.0435	44	4,160	616
6	2.300	80	0.0696	109	6,620	936
7 ^f	0.200	900	9.0000	57,800	206,000	19,100
8	2.240	100	0.0894	176	8,470	1,160

a. Complete computer data may be found in Appendix B.

b. Ratio of coating thickness to inside radius.

c. Maximum radial tension occurs at mid-plane position.

d. Maximum hoop tension occurs at inside surface; comparable compression exists at outside surface.

e. Maximum axial tension occurs at outside surface; comparable compression exists at the inside surface.

f. Extremely thick walled cylinder to prove that stresses to continue to increase as thickness to ratio increases.

not those which exist in as-deposited coated composites. However, these residual stresses which exist in pyrolytic graphite shells without regard for restraints from the substrate are of interest as background for the study of coated composites.

Several interesting conclusions can be drawn from the data in Table II. First, the radial tensile stresses, which might explain the delamination cracks which are most common in pyrolytic graphite, are not excessive for dimensions which are realistic for our nozzle study. An allowable radial tensile stress of about 1000 psi (across plane direction) is a reasonable value for pyrolytic graphite. Case 7 which was included to show the effect of a very thick shell of small inside diameter indicates that extremely high stresses would characterize such an unfavorable configuration.

In addition to the stress levels, the effect of the thickness (t) to inside radius (r_i) ratio on the stresses is of interest. Cases 2 and 8 indicate that geometric similarity leads to equal stresses in thin shells. The stress in each coordinate direction increases with increasing t/r_i ratio but not in the same manner. Over the range of t/r_i ratios typical of the nozzles for this program, the following observations can be made:

- (1) the hoop stress increases essentially in proportion to the increase in t/r_i ,
- (2) the axial stress increases with increased t/r_i but at a rate of less than proportional to the increase in t/r_i , and
- (3) the radial stress increases with increased t/r_i but at a rate greater than proportional to the increase in t/r_i .

3. Coated Composites

The nozzles under study in this program were all coated composites consisting of a coating of pyrolytic graphite as-deposited on the inner surface of a commercial graphite substrate. Since the pyrolytic graphite was to be used as an as-deposited coating, the stresses calculated for the composite are of greater interest than those calculated for free-standing shells. In any pyrolytic graphite coated body some mismatch of thermal expansion coefficients exists between the coating and the substrate in one or more directions. The elastic properties of the substrate graphite also generally differ from those of pyrolytic graphite. Each of these differences, in addition to the anisotropic nature of the pyrolytic graphite, contributes to the residual stress in a coated part. Again, these stresses cannot generally be eliminated but their identification is important. Effective control of the magnitude of these stresses is possible by the proper selection of geometrical factors and the properties of the substrate material.

Three series of stress calculations were made for coated composites consisting of a long cylindrical configuration. In a long cylinder, only

principal stresses exist and no shear stresses are developed. The selection of this configuration was necessary to avoid the mathematical complication of edge discontinuities which are involved in short cylinders. Thus, these calculations represent a partial solution and simplification of the stress pattern in actual coated inserts. However, valuable insight was gained into the nature of the stresses and the relation of these stresses to the geometry and materials selected for coated inserts.

a. Coatings on Inner Surface of Cylinder

In the first series of calculations, the stresses were computed for composites consisting of a pyrolytic graphite coating on the inner surface of a cylindrical substrate. Twenty-four cases were analyzed to determine the stress levels for all combinations of the following variables:

- (1) pyrolytic graphite thickness - 30, 50 and 80 mils,
- (2) substrate thickness - 0.40 and 0.70 inch,
- (3) substrate type - molded and extruded graphite,
- (4) inside diameter - 1.120 and 2.300 inch.

Table III contains a summary of the results of these calculations. Only the maximum principal tensile stresses are listed although compressive stresses of similar magnitudes are present. No failures which appear to be the direct consequence of compressive stresses have been noted in the experimental work. A complete presentation of the results of these stress calculations is included in Appendix C. The reader who is interested in further comparisons or study of these results is referred to this tabulation.

Examination of Table III illustrates a number of interesting factors. For a given type and size of substrate the radial tensile stress increases with coating thickness. For substrates of the same size, the radial tensile stresses for an extruded graphite substrate exceed those for a molded graphite. The magnitude of these radial tensile stresses are particularly important because they could explain delamination cracks. For a number of the configurations listed in Table III the maximum hoop tensile stress in the coating becomes quite large. Only in the case of the thicker coatings on the smaller substrate, however, does this hoop stress approach the value generally reported for the tensile strength of pyrolytic graphite in the a-b direction.

The axial stresses in the coating are entirely compressive. The tensile stresses in the axial direction in the substrate, however, are indicative of the forces created by the mismatch of the coating and the substrate in the axial dimension. The axial tensile stresses in the substrate increase with coating thickness and decrease with substrate thickness. For the cases selected, the axial stresses are somewhat larger in the large diameter substrate than in the smaller diameter substrate. The axial stress

Table III. Summary of Residual Stresses in Cylindrical Composites with Pyrolytic Graphite Coatings on the Inside.^a

Spec. No. ^a	Substrate Graphite Type	Inside Diameter of Composite (inch)	Substrate Wall Thickness (inch)	Coating Thickness (mil)	Max. Tensile Stresses in Coating			Max. Tensile Stresses in Substrate		
					Radial (psi)	Hoop (psi)	Axial (psi)	Radial (psi)	Hoop (psi)	Axial (psi)
1	Molded	1.120	0.400	30	None	None	None	None	639.	1,150.
2	"	"	"	50	32.2	3,370.	"	"	701.	1,763.
3	"	"	"	80	277.	10,170.	"	"	497.	2,486.
4	"	"	0.700	30	None	None	"	"	448.	592.
5	"	"	"	50	38.9	3,670.	"	"	457.	949.
6	"	"	"	80	305.	10,610.	"	"	231.	1,418.
7	"	2.300	0.400	30	None	None	"	"	724.	1,296.
8	"	"	"	50	None	None	"	"	1,013.	1,979.
9	"	"	"	80	0.9	557.	"	"	1,243.	2,800.
10	"	"	0.700	30	None	None	"	"	469.	716.
11	"	"	"	50	None	None	"	"	651	1,138.
12	"	"	"	80	1.1	603.	"	None	785.	1,694.
13	Extruded	1.120	0.400	30	13.1	2,200.	"	128.	1,925.	1,193.
14	"	"	"	50	137.	7,240.	"	147.	1,730.	1,499.
15	"	"	"	80	489.	14,020.	"	153.	1,200.	1,835.
16	"	"	0.700	30	57.6	4,630.	"	397.	2,686.	1,259.
17	"	"	"	50	238.	9,580.	"	424.	2,400.	1,424.
18	"	"	"	80	659.	16,320.	"	566.	1,807.	1,627.
19	"	2.300	0.400	30	None	None	"	10.	1,427.	908.
20	"	"	"	50	None	None	"	3.	1,571	1,351.
21	"	"	"	80	24.0	3,000	"	1.	1,593	1,783.
22	"	"	0.700	30	None	None	"	95.	1,757.	893.
23	"	"	"	50	None	162.	"	85.	1,800.	1,111.
24	"	"	"	80	43.7	4,040.	None	84.	1,740	1,396.

a. Complete computer data may be found in Appendix G.

is important in coated composites because in actual nozzle inserts edge effects come into play which yield secondary stresses in the composite. The transfer of axial stresses across the interface between the coating and the substrate in actual sections of finite length creates shear stresses. It is likely that these shear stresses, which are inter-laminar in nature for the coating, are one cause of the delamination flaws. The analysis of these shear stresses was not carried out in this program as indicated above because of the difficulty of such analysis. However, it is estimated that the magnitude of the shear stresses is related directly to the magnitude of the axial tension in the substrate.

Finally, examination of the hoop tensile stresses in the substrate indicates another potential problem area. In the cases involving the molded graphite, the hoop tension in the substrate appears safe since the tensile strength of molded graphite is of the order of 3000 psi. However, the tensile strength of extruded graphite, which may range from 1200 to 2000 psi, may not be sufficient to withstand the hoop or axial stresses. In fact, in the experimental deposition work, several instances of hoop stress failure occurred in extruded graphite substrates.

b. Coatings on Outer Surface of Cylinder

In the first series of calculations described above, the nozzle shape was idealized as a composite cylinder with the pyrolytic graphite coating on the inner surface. The cylinder was selected such that the circular cross-section was typical of a given nozzle throat plane. Thus, these previous calculations served to illustrate the effect of nozzle throat radius on coating stresses. To illustrate the effect of axial nozzle curvature on the stresses in the coated insert section, calculations were made for a composite cylinder with the coating on the outside with the cylinder radius equal to the radius of curvature of typical nozzles. Figure 6 shows pictorially the rationale behind this selection of geometry. The surface of an actual nozzle insert represents only a portion of a toroidal surface and thus does not consist of a closed surface along the direction of the radius of curvature. Nevertheless, it was felt that calculations for this outside coating geometry would help to indicate the effects of nozzle radius of curvature to supplement the calculation of the effects of nozzle throat diameter.

Twelve cases were calculated for coatings on the outside of a cylinder to demonstrate the effect of two radii of curvature, two thicknesses of a molded graphite substrate, and three pyrolytic graphite coating thicknesses. The maximum tensile stresses in each principal direction in both the coating and the substrate are listed in Table IV. Again only the maximum tensile stresses are listed although compressive stresses also exist. A complete tabulation of the stresses in each direction is included for each case in Appendix D. Examination of Table IV indicates that increasing the substrate thickness increases the radial tensile stress, but decreases the axial stress in the substrate. Increasing the radius of the substrate (i.e., the radius of curvature of the nozzle) decreases the stress levels. It was

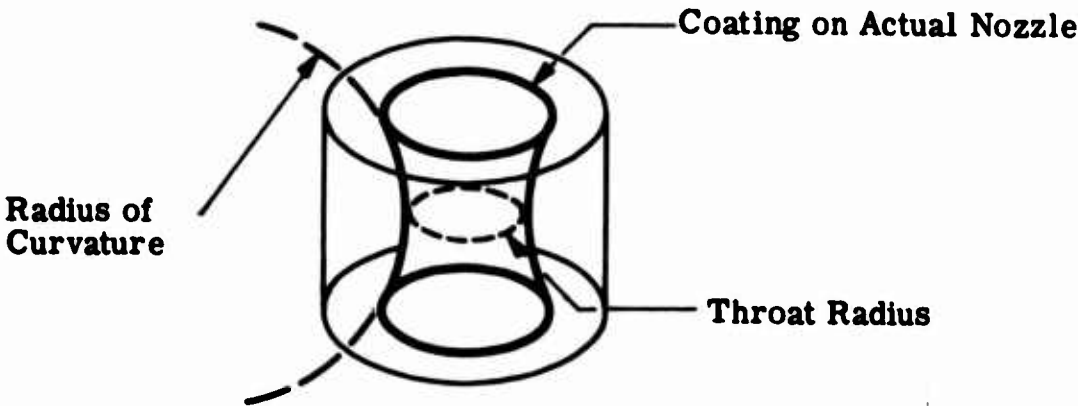


Figure 6. Pictorial Diagram Showing Parameters Related to Nozzle Slope.

Table IV. Summary of Residual Stresses in Cylindrical Composite with As-Deposited Pyrolytic Graphite Coatings on the Outside.^a

Case No. ^a	Coating Thickness (mil)	Maximum Tensile Stresses in Coating			Maximum Tensile Stresses in Substrate		
		Radial (psi)	Hoop (psi)	Axial (psi)	Radial (psi)	Hoop (psi)	Axial (psi)
A. Substrate radius = 1.600"; substrate thickness = 0.100"							
1	30	277	b	b	277	4440	2710
2	50	384			384	6210	3860
3	80	500			500	7900	5080
B. Substrate radius = 1.600"; substrate thickness = 0.400"							
4	30	382			382	1900	1050
5	50	610			610	2710	1580
6	80	925			925	3840	2290
C. Substrate radius = 3.200"; substrate thickness = 0.100"							
7	30	134			134	4300	2650
8	50	182			182	5820	3760
9	80	232			232	7370	4890
D. Substrate radius = 3.200"; substrate thickness = 0.400"							
10	30	188			188	1680	910
11	50	294			294	2470	1400
12	80	431			431	3510	2070

^a Complete computer data may be found in Appendix D.

b. Where no value is listed, stresses are entirely compressive.

not feasible because of design limitations and deposition problems, to investigate experimentally the apparent improvement gained by going to a larger radius of curvature. Furthermore, increasing the radius of curvature generally produces a rather severe penalty in a light-weight nozzle by increasing the length of the nozzle.

Several other interesting stress patterns are apparent from examining Table IV. The only tensile stresses in the coating are those in the radial direction. In the substrate, the radial tensile stresses are equal to those in the coating but both the hoop and axial stresses are also tensile. Both the hoop and axial stresses are quite high for the thinner substrates. Increasing the substrate thickness, of course, decreases both of these stress levels. As would be expected, increasing the coating thickness, other factors being equal, increases all the stress levels.

c. Effect of Substrate Properties

In the discussion above of the source of the stresses in pyrolytic graphite coated inserts, it was pointed out that residual stresses could not be eliminated. However, it is apparent that the properties of the substrate graphite will have a significant effect on the stress levels in both the coating and the substrate portion of a coated composite. In an effort to identify preferred substrate graphites, a series of calculations was made for a molded graphite (National Carbon ATJ), an anisotropic, high-density graphite (National Carbon ZTA), a low-modulus, fibrous graphite (National Carbon PT-0114), and an extruded graphite (Speer 580). Calculations of the stress levels in both substrate and coating layers were made for composite cylinders with the coating on the inside using two diameters, equivalent to the two nozzle sizes under study, and three coating thicknesses for each of the four substrate materials. The complete results of these calculations are tabulated in Appendix E. The input data used for these calculations are also tabulated with the results. The thermal expansion values used were somewhat different from those used in the earlier calculations. The data which were used in this last series of analyses were taken from the latest and most complete sources available in the literature. Therefore, for correlation of calculated stresses with experimental data these results are most reliable.

The results of this series of calculations are summarized in Table V. Various effects of the substrate properties are apparent from examination of this table. The stresses calculated for the molded graphite (ATJ) appear moderate except for two factors. As the coating thickness increases in relation to the diameter (e.g., Case 3), the radial and hoop stresses in the coating rise quite rapidly. This appears to be evidence of the internal anisotropy of the pyrolytic graphite which is not greatly modified by the ATJ substrate. Second, the axial stress in the substrate for 50 and 80 mil coatings is higher than for the other substrates compared in Table V. The shear stresses

Table V. Effect of Substrate Properties on Stresses in Composite Cylinders.

Case No. ^a	Inside Diameter (inch)	Coating Thickness (mil)	Maximum Tensile Stresses in Coating			Maximum Tensile Stresses in Substrate		
			Radial (psi)	Hoop (psi)	Axial (psi)	Radial (psi)	Hoop (psi)	Axial (psi)
A. Molded substrate (ATJ) 0.700" thick								
1	1.120	30	1.	638	b	b	322	567
2	1.120	50	93.	6010			262	900
3	1.120	80	425.	13,200		18		1310
4	2.300	30					380	680
5	2.300	50					505	1,070
6	2.300	80	18	2,670			565	1,560
B. High Density substrate (ZTA) (anisotropy same orientation as PG); 0.700" thick								
7	1.120	30	b	b	1,680		3,770	b
8	1.120	50					5,360	23
9	1.120	80					6,880	154
10	2.300	30				2,220	3,040	
11	2.300	50				655	4,580	
12	2.300	80					6,360	124

^a Complete computer data may be found in Appendix E.

^b Where no value is listed, stresses are entirely compressive.

Table V. (cont'd)

Case No. ^a	Inside Diameter (Inch)	Coating Thickness (mil)	Maximum Tensile Stresses in Coating			Maximum Tensile Stresses in Substrate		
			Radial (psi)	Hoop (psi)	Axial (psi)	Radial (psi)	Hoop (psi)	Axial (psi)
C. Molded Fibrous substrate (PT-0114); 0.700" thick								
13	1.120	30	111	6,830	b	74	b	189
14	1.120	50	271	10,800		154		256
15	1.120	80	608	16,500		280		310
16	2.300	30	22	2,980		9		220
17	2.300	50	61	5,050		28		297
18	2.300	80	151	8,040		66		363
D. Extruded substrate (Speer 580); 0.700" thick								
19	1.120	50	873	20,300	712	873	1080	896
20	1.120	80	1520	27,200	2200	1490		842
21	1.120	120	2500	35,700	4040	2290		712
22	2.300	50	243	10,400	17	268	791	516
23	2.300	80	440	14,100	749	439	287	506
24	2.300	120	750	18,700	1730	722		457

^a Complete computer data may be found in Appendix E.

^b Where no value is listed, stresses are entirely compressive.

which result from the axial force in actual insert sections of short length can explain the observed delamination flaws.

With the high density graphite (ZTA), the calculations show that the radial tension is eliminated and the axial tension in the substrate is greatly reduced or eliminated for all cases. Two major problems can be identified, however. First, the substrate hoop tension exceeds the material strength for all configurations. Consistent with this, the only coating deposited on ZTA graphite led to a hoop tension failure in the substrate. Second, the orientation of the substrate anisotropy cannot actually match the coating anisotropy orientation as assumed in the calculation since the ZTA is a molded graphite. The experimental substrate was cut with its axis across the molded billet so that the hoop and radial properties are alternately with-grain and across-grain at 90° intervals of rotation. Matching of the axial direction of the substrate with the with-grain direction of the ZTA, to provide the reduction in axial stresses, was achieved.

Perhaps the most significant results in Table V, at least for support of the firing tests in the current program, are those for the fibrous graphite (PT-0114). Each stress calculated, with the possible exception of the thickest coating on the subscale substrate appears to be of a tolerable magnitude. Experimental evidence confirms these predictions since coatings 51 mils thick on the subscale substrate and 100 mils thick on the fullscale substrate were deposited without stress failure. The calculated axial tension in the substrate is of the same order as the published cross-grain strength of the material (Ref. 11), but no evidence of substrate delamination was noted. It is quite possible that some permanent deformation of this type of substrate is possible without the appearance of discrete cracks. Although the low grade properties of fibrous graphite do not recommend it on first examination as the most desirable substrate, the use of this type of substrate did provide a useful advance in the technology of coated inserts for full-scale tests in this program. Further work will be required to determine whether another substrate selection would be optimum or whether the fibrous material does represent a preferred approach.

The extruded graphite (Speer 580) was selected because it had better-than-average strength properties for an extruded grade and an unusually low thermal expansion in the with-grain (axial) direction. The improved match in expansion in the axial direction leads to reduced axial tension in the substrate as seen in Table V. Both the radial and hoop stresses in the coating on this extruded graphite were calculated to be higher than for the molded (ATJ) substrate. Assuming a dual criterion for coating integrity, namely, low radial stress in the coating and low axial stress in the substrate, the calculations predict qualitatively the observed results for coatings deposited on Speer 580 graphite. Coatings up to 47 mils in thickness were uncracked, but at 64-mil thickness delamination cracks were noted. It should be noted that because of the interest in thicker coatings for the final fullscale motor firing,

the coating thickness considered for the calculations in Table V for the Speer 580 was increased to 120 mils. A more detailed comparison of the calculated stresses in coated inserts with experimental observation of delamination cracks is made after the description of the deposition studies in the next section of this report.

4.0 DEPOSITION STUDIES

A. GENERAL

Rocket motor firing tests were the basis of the feasibility demonstration of pyrolytic graphite coated nozzles. However, no motor firings could be achieved without the prior preparation of suitable inserts. All of the inserts tested in this program were fabricated in the laboratories of Atlantic Research Corporation. The integration of the deposition studies and the motor test evaluation work was a very distinct advantage in this program. Deposition work was carried forward until inserts suitable for testing were produced. Following the test in a motor firing of a given insert, it was possible to return immediately to the deposition study in order to prepare further and improved coated inserts. In this way, the maximum feedback of information from the evaluation phase was available to guide the deposition work.

The equipment and procedures used in the deposition of pyrolytic graphite coatings was fully described in Reference 1. All of the coatings were deposited at a substrate temperature of 2000°C with methane as the carbonaceous source gas. The density of coatings prepared under these conditions is typically 2.17 gm/cu cm. X-ray diffraction indicates typical values as follows:

$$d\text{-spacing} = 3.45 \text{ \AA}$$

$$\text{crystallite size: } L_c = 75\text{\AA}; L_a = 120\text{\AA}$$

The deposition conditions which were varied to control the nature and thickness of the coatings included the flow geometry, the flow rates, and the deposition time. Deposition work was carried out to prepare subscale inserts of nominal 1.1-inch throat diameter and fullscale inserts of nominal 2.3-inch diameter. The results of the deposition study in each size range are discussed separately.

B. SUBSCALE INSERTS

The initial deposition work was carried out with subscale inserts. Since the basic design of the test nozzle utilized an insert segment coated with pyrolytic graphite which was only long enough to provide the required dimensional stability at the throat of the nozzle, an excellent opportunity existed to study the quality of the coated insert at both the upstream and downstream edges of the insert. The examination of the microstructure and quality of the coating was carried out by microscopic examination of the polished cross-section. This examination is indispensable if the performance of the nozzle is to be related to the pre-firing condition.

The radius of curvature of the subscale insert was chosen to be three times the nominal throat radius. The length of the coated insert was

selected as 1.22 inches so that the inlet joint fell at an area ratio of 2 relative to the throat and the outlet joint occurred at the 15° tangent point to match the expansion cone half angle. Several coated inserts were prepared on molded graphite substrates of this configuration prior to the first motor test. In each insert, significant delamination cracking was found at the exit end of the coating during microscopic examination. The cracks were always in the coating, never at the substrate surface. These cracks often originated during the machining of the insert piece from the coated substrate tube but changes in machining practice did not eliminate the cracks. When initial changes in the deposition conditions failed to eliminate these cracks, it was decided to motor test a typical insert containing a delamination crack at the exit end. The microstructure of both the inlet and exit end of the coated insert selected for the first subscale firing is shown in Figure 7. The crack in the exit end which averaged about 1 mil in width and was about 10 to 15 mils above the substrate is typical of all those observed in the subscale insert deposition work.

The cracking observed in the initial coatings on subscale inserts was always at the exit end of the insert and seemed to be aggravated by the machining operation following deposition. Therefore, a modification of the substrate design was made so that no machining was required at the exit end of the coated section following deposition. A small wrap-around section of the coating at the exit end prevented microscopic examination of the coating there, but a partial crack at the inlet end of the test section was noted. To compare the effect of the stress relief crack at the inlet with the crack at the exit end, this insert was selected for the second subscale motor test.

The next modification in the deposition work for subscale inserts consisted of the use of an extruded graphite substrate. The improved match of thermal expansion coefficients in the axial direction was expected to improve the crack resistance of the coating. A flaw-free coating was prepared on an extruded graphite substrate, but during final machining on the outside diameter of the substrate, a hoop tensile failure occurred in the substrate because of the lower strength of the extruded graphite in this direction. This substrate failure propagated into the coating and caused it to crack also. At this point in the subscale program, the use of extruded graphite substrates was set aside in favor of other process modifications. Only a limited number of subscale inserts were required so that success with other process modifications prevented the return to the study of extruded graphite. Thus, the possibility of preparing coatings on subscale substrates of extruded graphite was not fully exploited.

Success had been achieved in an earlier program (Ref. 1) in preparing crack-free inserts of a size almost identical to the current subscale design. A re-study of these deposits indicated a subtle variation in coating structure especially in the exit end of the nozzle where the current problem with delamination flaws was most prevalent. By following this line of attack and making further changes in the process conditions, a steady



a. Entrance (X150)



b. Exit (X150)

2752

Figure 7. Microstructure of Pyrolytic Graphite Coating on Insert for Subscale Firing Number 1.

advance in our capability to prepare flaw-free coatings was made in the subscale system. The first flaw-free coated insert prepared and fully machined for firing had a coating thickness of approximately 23 mils at the throat. The microstructure of this coating, which was successfully tested in subscale Firing No. 3, is shown in Figure 8. The increased renucleation in this coating is apparent compared to that in Figure 7.


Following the preparation of this relatively thin crack-free coating deposition work continued along the same line and crack-free coatings as thick as 54 mils were successfully deposited on subscale molded graphite substrates. The microstructure of the 54-mil coating, tested in subscale Firing No. 4 is shown in Figure 9. The upper limit of coating thickness which can be made by the preferred deposition technique with a molded graphite substrate of the subscale configuration was not determined since the requirements of the motor test program for test nozzles was fulfilled before this limit was reached. The requirement for fullscale inserts then took precedence over further laboratory study on subscale inserts. The fact that discrete coating losses occurred during motor test of the 54-mil-thick coating, as discussed later in this report (Section 5.B.4.), suggests that the upper limit was at hand. The residual stresses plus the stress factors associated with the nozzle conditions apparently led to progressive coating failure.

Prior to the completion of the subscale deposition work, enough study of the deposition process for fullscale inserts was completed to indicate that significant problems could be anticipated in preparing flaw-free coatings of sufficient thickness for full duration motor firings. Thus, the final work on subscale deposition consisted of an exploratory test of the suitability of a low modulus, fibrous graphite as a substrate material. A flaw-free coating 51 mils thick was deposited on a fibrous substrate. More important for the timely pursuit of the program objectives, this coated insert was successfully tested on subscale motor Firing No. 5, as described below in Section 5.B.5.

C. FULLSCALE INSERTS

Deposition studies with fullscale substrates were started during the fourth month of the program and were continued for the remainder of the program. Thus, during the middle of the contract period subscale and fullscale deposition work proceeded concurrently. This approach was adopted so that maximum use could be made of the information gained in the deposition work. Deposition procedures suitable to only one size insert were thus avoided.

In the preparation of fullscale inserts the substrate system was segmented so that the insert was separate from the inlet and outlet sections. This design reduced the amount of machining required on the coated insert and thus largely eliminated this possible source of damage to the coatings.

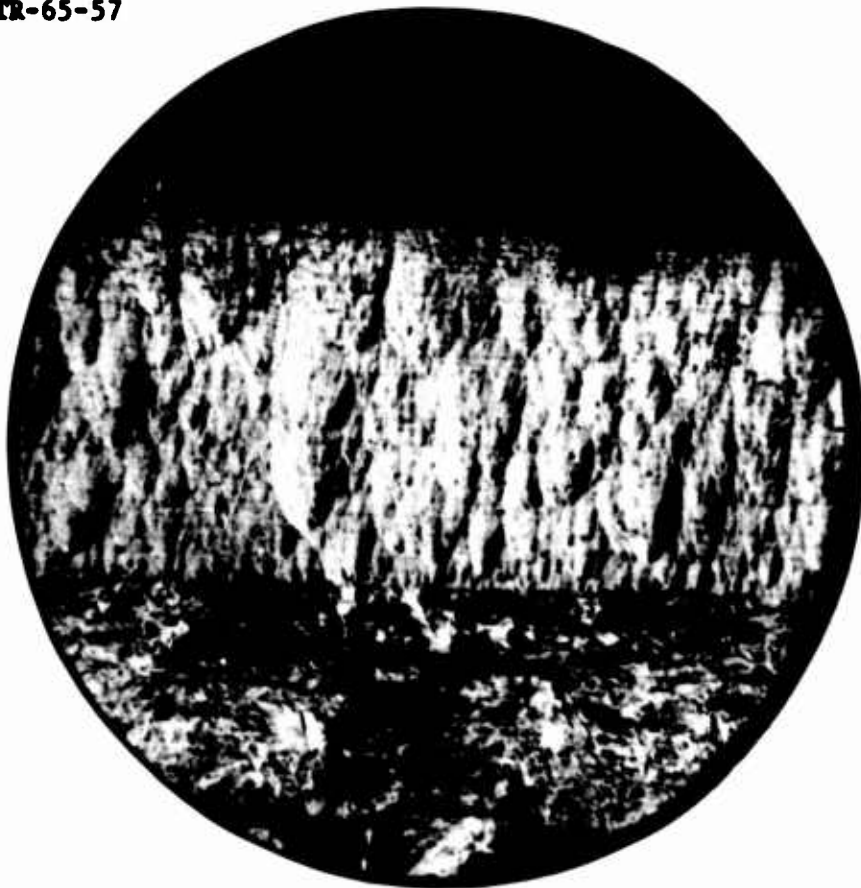

AR 2757

Figure 8. Microsturcture of Pyrolytic Graphite Coating at Entrance of Insert for Subscale Firing Number 3 (X150).



a. Entrance (X60)



b. Exit (X150)

AP 2755

Figure 9. Microstructure of Pyrolytic Graphite Coating on Insert for Subscale Firing Number 4.

For the larger scale pieces this design also provided a significant cost reduction in preparation of the fixtures.

In the initial deposition work with fullscale inserts, delamination cracks were observed at coating thickness of the same order of magnitude as those which led to cracks in the subscale coatings. At first this was somewhat surprising since, in general, the principal stresses caused by coating anisotropy are roughly a function of the ratio of coating thickness to radius of curvature rather than to the absolute value of the coating thickness. However, stresses produced by mismatch of substrate and coating expansion properties are more nearly dependent on the linear measurements of the composite. Thus, the observed behavior suggests a dominate role of thermal expansion stresses in the delamination phenomenon.

A qualitative observation of note made on the early fullscale inserts was that the nature of the cracking was somewhat different from that seen on the subscale inserts. On the fullscale inserts cracking occurred largely at or very near the substrate-coating interface. On the subscale inserts the cracks were generally completely within the coating, most often two-tenths or more of the coating thickness away from the interface.

Prior to the achievement of flaw-free fullscale coatings of usable thickness, one insert containing a typical microscopic delamination separation at the exit end was selected for motor test. The microstructure of this coating at each end is shown in Figure 10.

The observations regarding delamination cracks in fullscale coatings led to emphasis on two factors in the deposition work. First, to achieve maximum bond strength a thermal pretreatment of the substrate was adopted. This pretreatment was performed following all machining operation just prior to the deposition run. A sooty layer on the surface was found on some inserts following pretreatment and that would likely be detrimental to the coating-substrate bond. The substrate was dry polished following pretreatment to provide a clean deposition surface.

The second factor emphasized to improve the integrity of fullscale coatings was the selection of different grades of graphite as substrates in an effort to improve the compatibility of coating and substrate. The use of an extruded graphite (Speer 580) provided sufficient relief for the incompatibility problem (principally in the axial or with-grain direction) so that a flaw-free coating 47 mils thick was prepared. The microstructure of this coating, which was motor tested in fullscale Firing No. 2, is shown in Figure 11. A similar coating of 64 mils thickness on the Speer 580 contained a delamination crack.

To achieve still thicker coatings without cracks, substrates were machined from a low modulus, fibrous graphite (National Carbon PT-0114).

AFRPL-TR-65-57




a. Entrance (X150)



b. Exit (X150)

2756

Figure 10. Microstructure of Pyrolytic Graphite Coating on Insert for Fullscale Firing Number 1.

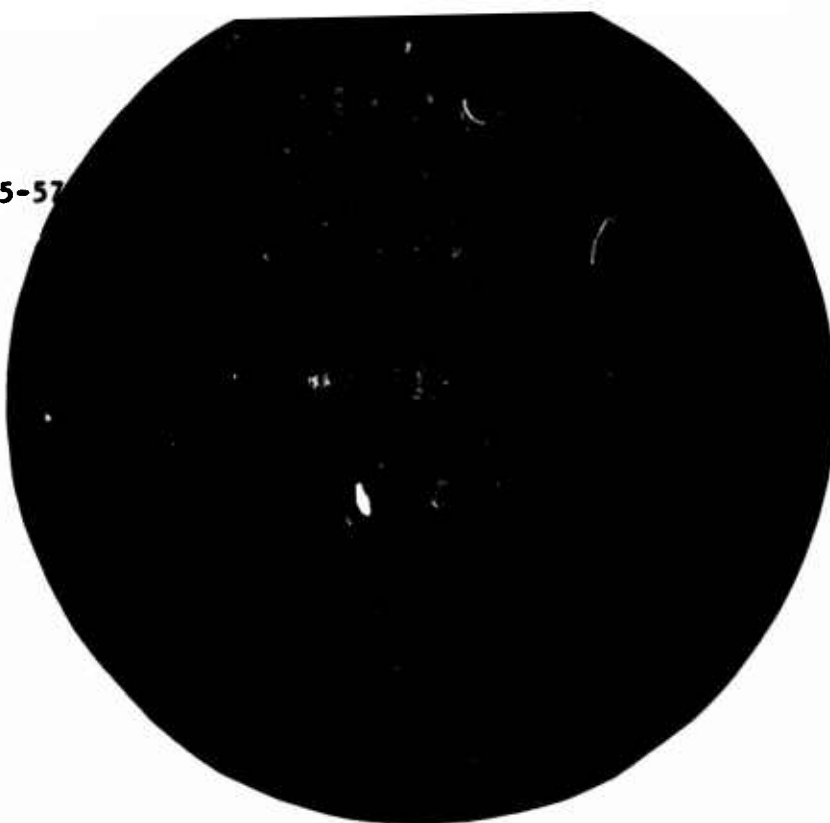

a. Fullscale Firing Number 2; Exit (X150)



b. Fullscale Firing Number 3; Exit (X150)

AP 2751

Figure 11. Microstructure of Pyrolytic Graphite Coating on Insert for Fullscale Firings Number 2 and Number 3.

Pyrolytic graphite coatings as thick as 100 mils were successfully deposited on this type of substrate material without observable delamination cracks. A coating of 75 mils thickness on the fibrous graphite substrate was selected for test in fullscale Firing No. 3. The microstructure of this coating is shown in Figure 11.

The thickest coating prepared on this program, which was also deposited on the fibrous type substrate, was selected for fullscale Firing No. 4. The microstructure typical of this coating is illustrated in Figure 12. The as-deposited coating, which was 101 mils thick, contained a number of nodules which had grown to various sizes up to the order of a tenth of an inch in diameter. Microscopic examination of the polished edge of the coating revealed that the local flaws in these nodules, which are characteristic of any nodule, were more severe than usual. Because of the surface roughness introduced by these nodules, the surface was hand-polished prior to motor test. To define the effect of this polishing operation in the area of the local flaws, photomicrographs were made both before and after this smoothing step. Views of typical nodule regions both as deposited and after surface polishing are shown in Figure 13. It is apparent that the polishing did not significantly interact with the pre-existing local flaws except that it allowed some of these flaws to be exposed at the finished surface. The local flaws lie along the locally distorted direction of the pyrolytic graphite layer planes. Polishing the surface in the region of a nodule cuts across the layer planes locally and consequently exposes the edge of the planes in these areas. The role of local flaws in increasing the erosion rate of a pyrolytic graphite coating was not determined quantitatively, but qualitatively it can be surmised that some loss in erosion resistance is inevitable. This assumption was borne out in the results of the fourth fullscale firing described later. Optimization of the coating structure and reduction of the nodule population were beyond the scope of this feasibility program but the incentive for such an effort was indicated.

D. CORRELATION OF RESIDUAL STRESSES AND OBSERVED CRACKS

In the preceding major section of this report, the residual stresses calculated for coated composites were presented. In this section, the experimental evidence of delamination cracking was outlined. In Table VI, the data pertinent to the establishment of failure stress criteria are summarized. Two calculated stress values, the radial tension in the coating and the axial tension in the substrate, are listed for the thickest crack-free coatings and the thinnest coatings which contained cracks for each substrate material used. As outlined in the introduction to the stress analysis discussion, the two types of tensile stress listed are those which are consistent with the nature of the cracks observed. Examination of Table VI indicates failure criteria which are consistent with all the



a. Entrance (X150)



b. Exit (X150)

2754

Figure 12. Microstructure of Pyrolytic Graphite Coating on Insert for Fullscale Firing Number 4.



a. As Deposited (X60)



b. After Surface Polishing (X60)

2753

Figure 13. Local Flaws Associated with Nodules in Coating on Insert for Fullscale Firing Number 4.

**Correlation of Calculated Stresses
and Observed Delamination Cracks**

Substrate Type	Coating Thickness (mil)	Cracks	Calculated Stresses*	
			Radial in Coating (psi)	Axial in Substrate (psi)
<u>A. Subscale, 1.12 inch Diameter</u>				
ATJ	54	No**	100	<u>950</u>
Fibrous	51	No	280	260
<u>B. Fullscale, 2.30 inch Diameter</u>				
ATJ	22	No	Compressive	520
ATJ	42	Yes	Compressive	<u>920</u>
580	47	No	220	520
580	64	Yes	<u>340</u>	510
Fibrous	100	No	230	400

* Interpolated and extrapolated from data in Table V.

** No cracks observed, but coating failed during motor test.

experimental evidence gathered. The stress values underlined in the table are called to the reader's attention as those which appear critical. A radial tensile stress level in the coating between 280 and 340 psi separates the crack-free and cracked condition. An axial tensile stress in the substrate between 520 and 920 psi appears critical. In the case of the 54-mil coating on the subscale ATJ substrate, no cracks were observed although the axial tension in the substrate was calculated to be 950 psi. However, this coating failed and was removed during motor test which suggests a residual stress condition close to the failure level.

Although the absolute values of the failure stresses indicated are subject to the approximations involved in the calculations, the discovery of a self-consistent body of calculated and experimental evidence on delamination cracking is significant. Optimization of fabrication technology can be pursued by reduction of the residual stresses or by increasing the tolerance of the pyrolytic graphite for these stresses. The advances achieved in the deposition work on this program came from work along both of these paths, but further advances should be possible beyond the scope of this program.

5.0 MOTOR FIRING TESTS

The focal point of the entire program to determine the feasibility of pyrolytic graphite coated nozzle inserts was the motor firing evaluation. To prove the feasibility of a nozzle material, critical motor firing tests must be completed successfully. The goal of this program was to prove the suitability of a pyrolytic graphite coated nozzle for service with a 6550° F propellant and a motor pressure of 700 psi in a reasonably size system and for a realistic firing duration. To achieve this goal, in addition to the analytical and deposition work described elsewhere, a series of subscale and fullscale motor firings was carried out. The subscale motor firings using a nozzle of 1.1-inch throat diameter for a motor of approximately 1100 pounds thrust were carried out to define the suitability of the basic design and material for critical nozzle service. Following the subscale effort, a series of fullscale firings using a nozzle of 2.3-inch throat diameter with a motor of approximately 4600 pounds thrust was carried out to demonstrate usable service in sufficiently large nozzles to be indicative of the merit of pyrolytic graphite coating. In the following sections, the motor firing procedures and the results of the subscale and fullscale firings are discussed separately.

A. TEST PROCEDURE

The motors used for both subscale and fullscale nozzle tests were of an insulated heavy-weight design and were filled with gel propellant. The use of gel propellant and a heavy-weight motor design leads to a minimum cost program of nozzle materials evaluation. The propellant used in all firings in this program was a highly aluminized solid propellant having a theoretical flame temperature of 6550° F and moderately oxidizing combustion products. This propellant is designated at Atlantic Research as APG-112. The characteristics of this propellant are summarized in Table VII.

Each test nozzle was fabricated and assembled in our laboratory and shops and then transported to the rocket test bay. Figure 14 is a photograph of the fullscale test motor in operation. The level of the motor pressure and changes in the motor pressure along with pre- and post-firing measurements and examinations define the erosion performance of a nozzle material. Thermocouple instrumentation was placed on the first nozzle tested to confirm the design selection but temperature instrumentation was not used on later tests.

B. SUBSCALE MOTOR FIRINGS

A total of five subscale evaluation tests were successfully completed. The design philosophy for both the subscale and fullscale nozzles utilized the segmented concept in which the pyrolytic graphite coated insert was only a segment large enough to provide dimensional stability at the throat. A number of other segments were used to form the total nozzle contour and support, back-up, and insulate the exposed segments. The basic design used in all of the subscale nozzles is shown in the

CONFIDENTIAL

AFRPL-TR-65-57

Table VII. Characteristics of APG-112 Propellant

	CHAMBER	EXHAUST
Specific Impulse (lb-sec/lb)	262.4	
Characteristic exhaust velocity (ft/sec)	5042	
Temperature (°K)	3894	2719
Specific Heat (cal/100g-°K)	44.26	42.96
Moles of gas (g moles/100g)	2.9833	2.7849
Pressure (psia)	1000	14.699
<u>Combustion Products</u>		
g moles/100g		
C	0.0000	0.0000
H	0.2678	0.1057
O	0.0074	0.0003
N	0.001	0.0000
Cl	0.0648	0.0333
Al	0.0121	0.0003
CO	0.5403	0.5465
CO ₂	0.0191	0.0128
CN	0.0000	0.0000
HCN	0.0000	0.0000
H ₂	0.9790	1.1281
H ₂ O	0.2909	0.1758
HCl	0.3494	0.4904
O ₂	0.0009	0.0000
OH	0.0492	0.0048
N ₂	0.2659	0.2682
NO	0.0042	0.0002
NH	0.0003	0.0000
NH ₂	0.0001	0.0000
NH ₃	0.0000	0.0000
Cl ₂	0.0001	0.0000


CONFIDENTIAL

AFRPL-TR-65-57

Table VII. (Continued)

Combustion Products

AlH	0.0017	0.0000
AlO	0.0045	0.0000
Al ₂ O	0.0023	0.0000
Al ₂ O ₂	0.0003	0.0000
AlCl	0.1112	0.0168
AlCl ₂	0.0051	0.0010
AlCl ₃	0.0006	0.0002
AlOCl	0.0059	0.0004
C (solid)	0.0000	0.0000
Al ₂ O ₃ (liquid)	0.4335	0.4973
Al ₂ O ₃ (solid)	0.0000	0.0000
AlN (solid)	0.0000	0.0000

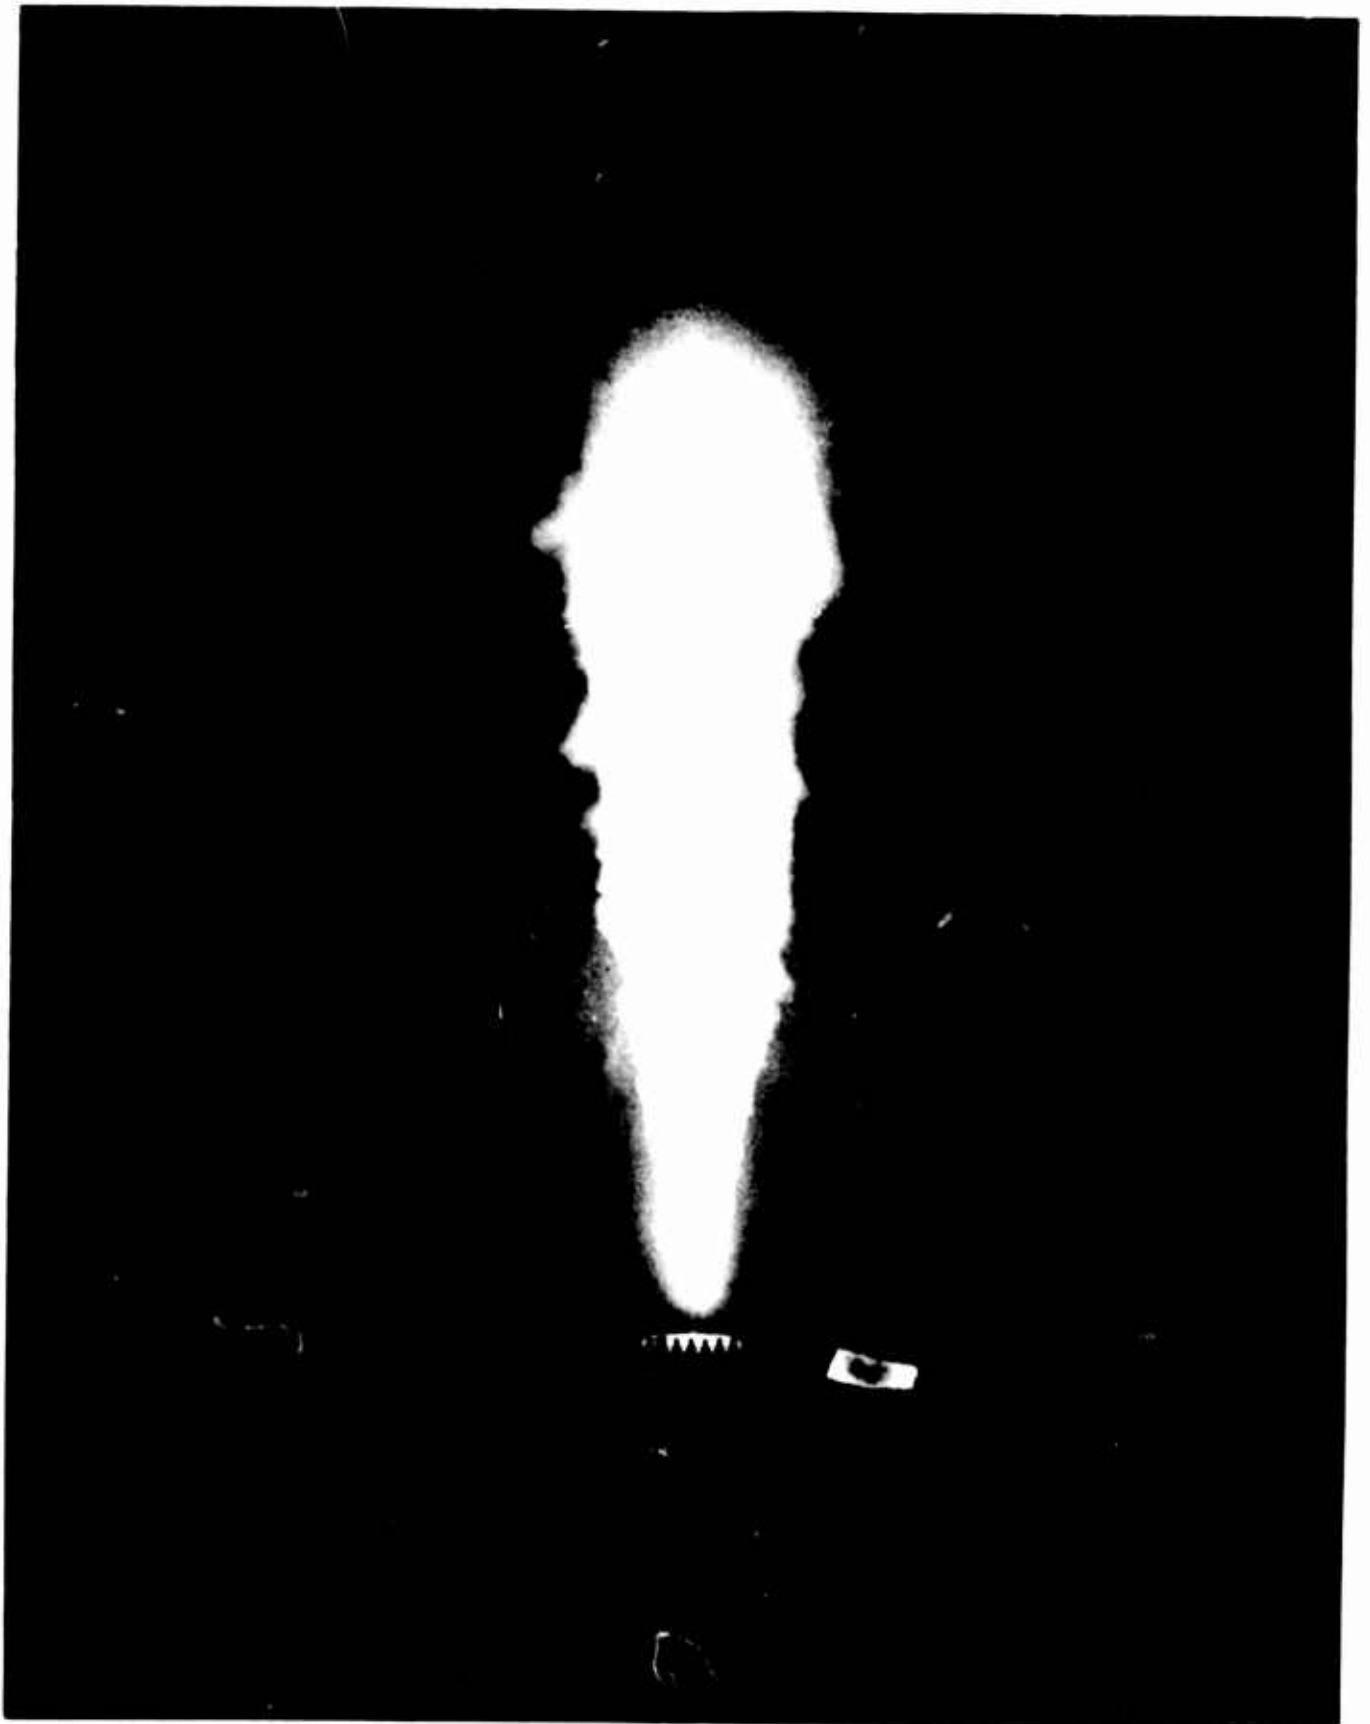

2654

Figure 14. Fullscale Test Motor During Firing.

assembly drawing, Figure 15. The actual segments used in one of the subscale nozzles are pictured prior to assembly in Figure 16.

For the subscale nozzles the radius of curvature of the insert substrate was chosen to be approximately three times the throat radius. The length of the coated insert was selected so that the joint line at the inlet end was at an area ratio of 2 relative to the throat, and the exit joint line occurred at the 15° tangent point to match the expansion cone half angle. Previous work had indicated the desirability of protecting the inlet edge of the coated insert from excessive exposure to the flow of combustion gases. For convenience in this program, a single plate of pyrolytic graphite in the edge-oriented position was placed immediately upstream of the pyrolytic graphite coated throat insert. In a flight-weight nozzle design, the optimum selection for the entrance section might well be a second pyrolytic graphite coated segment. For the test nozzles in this program the pyrolytic graphite plate and the insulation thicknesses were selected to provide nozzle integrity in accordance with the results of the thermal analysis discussed in another section.

To provide for the thermal expansion of the exposed segments in each test nozzle, calculations were made of the expansion to be expected from each segment so that expansion joints could be installed at selected locations. The total expansion of each of the exposed segments shown in the assembly drawing, Figure 15 was calculated as follows:

- (1) Entrance section 1 - 19 mils.
- (2) Entrance section 2 - 25 mils.
- (3) Throat section - 16 mils.
- (4) First exit section - 18 mils.
- (5) Exit cone - 39 mils

To accommodate these expansions the following design decisions were made:

- (1) The expansion of the first inlet section would be taken by the shrinkage and crushing of the reinforced plastic at the nozzle entrance.
- (2) An expansion joint 30 mils thick was placed at the entrance end of the second entrance section to accommodate 50 per cent of the total expansion of the second, third and fourth segments of the nozzle. A silicone rubber expansion gasket was used at this upstream location in all tests.

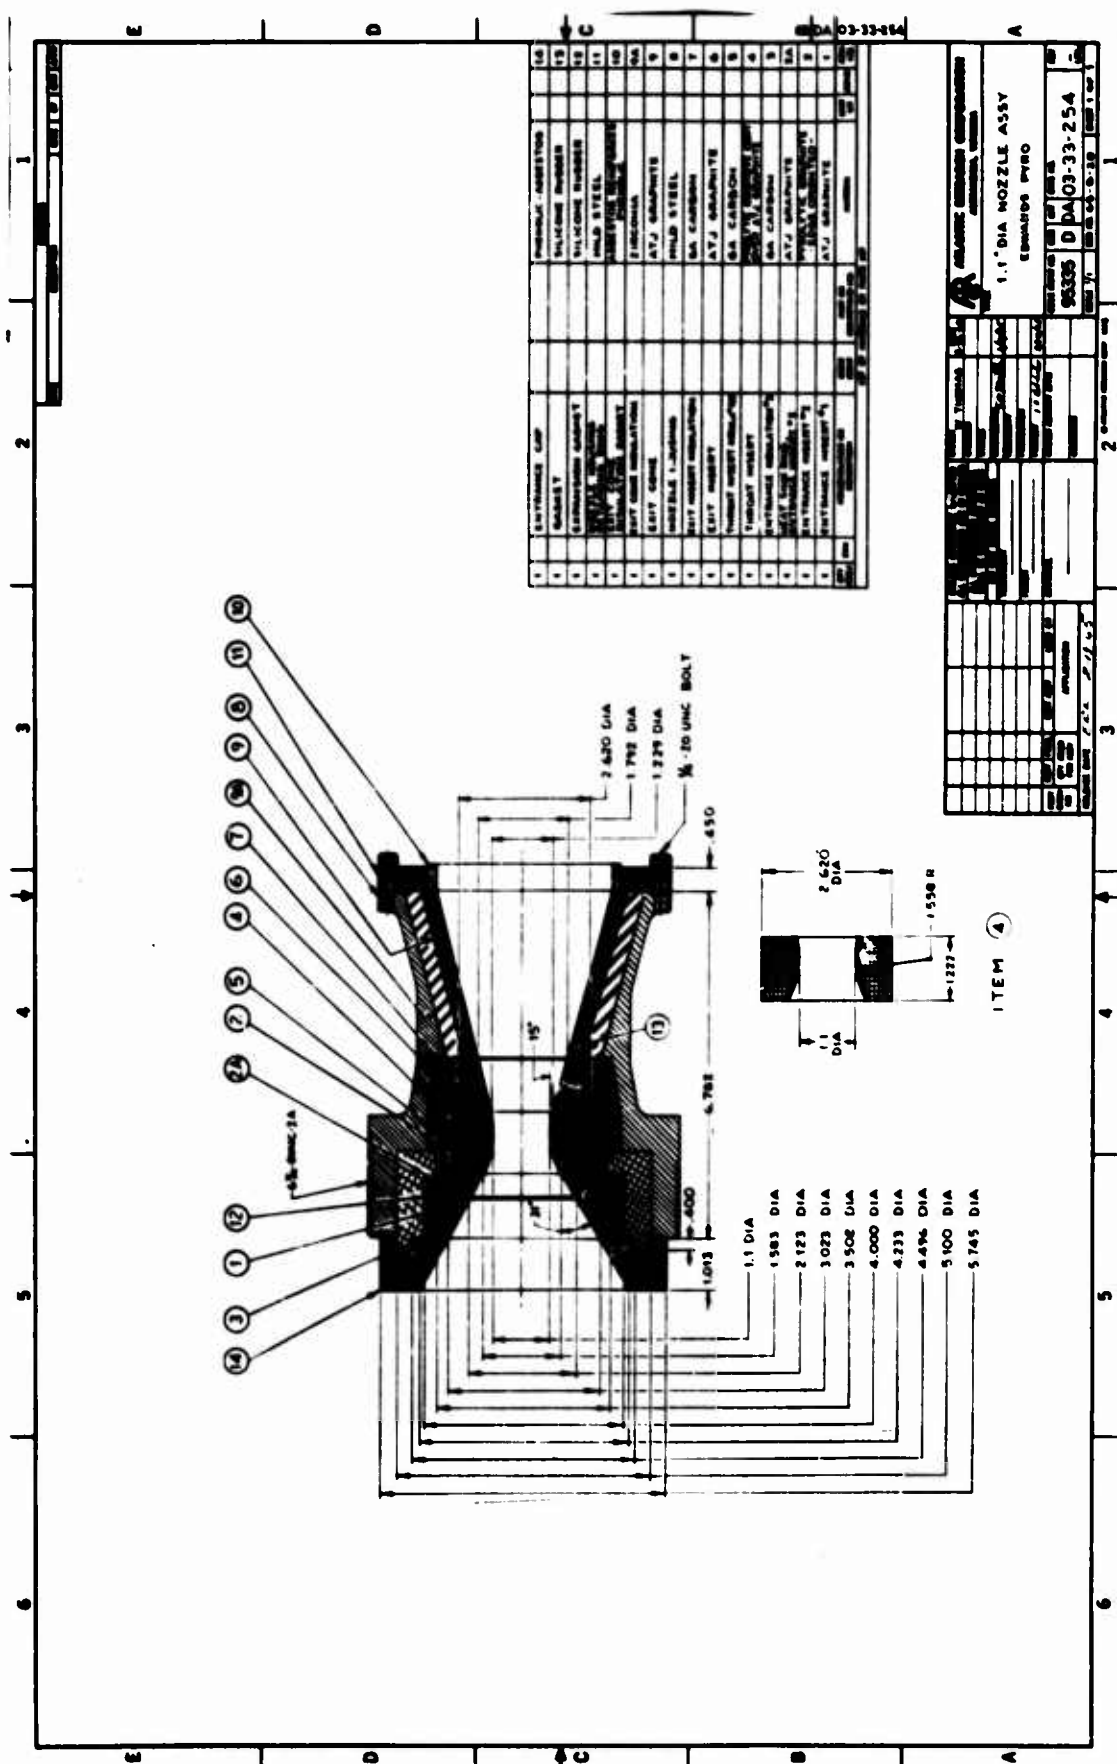


Figure 15. Subscale Nozzle Assembly Drawing.

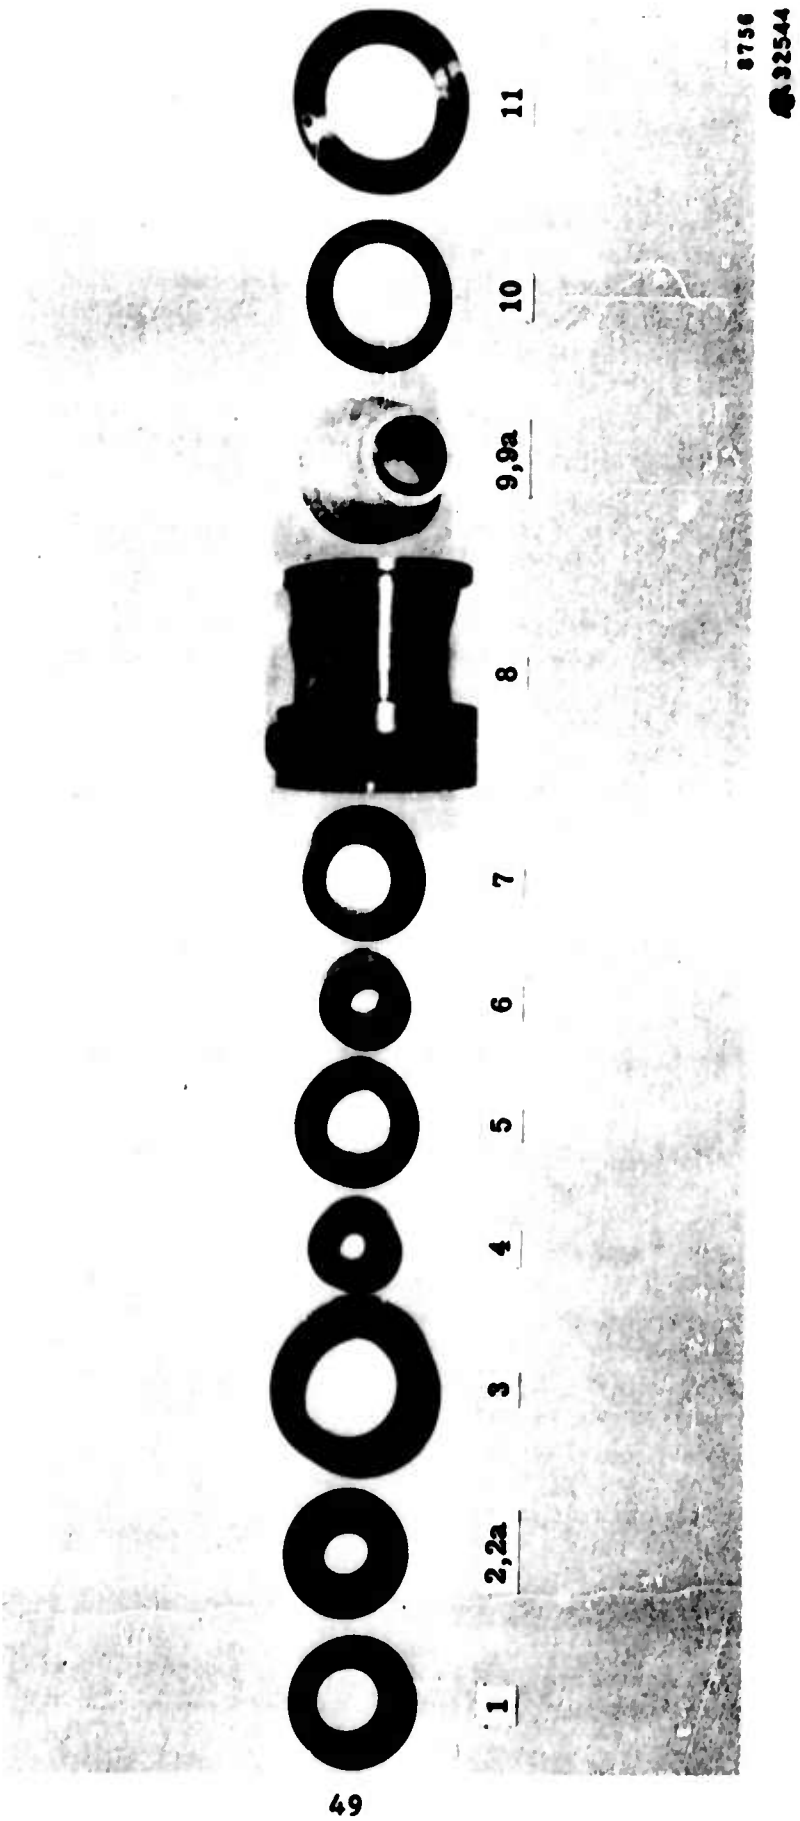


Figure 16. Components of Subscale Nozzle Prior to Assembly.

CONFIDENTIAL

AFRPL-TR-65-57

(3) A second expansion joint between the fourth and fifth segment might be required to accommodate the expansion in this region. The second expansion joint utilized in the first test was found unnecessary and eliminated in subsequent tests. (U)

A summary of all of the evaluation data obtained in the motor test firings is contained in Table VIII. In the following sections, each of the subscale firings is described and discussed separately, and then a comparison and discussion of the implications of these firings is presented. (U)

1. Subscale Firing No. 1

The first subscale firing was carried out prior to the point in the deposition study when delamination flaws were eliminated. The insert selected for this test had a coating thickness of 58 mils at the throat and contained a microscopic delamination at the exit end of the insert. Nozzle erosion during this test was smooth as can be seen from the motor pressure trace in Figure 17, but the rate of erosion was greater than that predicted for a good coating. The erosion was sufficient to remove the entire coating during the 56 second duration at an average motor pressure of 564 psi. Figure 18 shows that although insert erosion was higher than desirable, the general condition of the remainder of the nozzle was satisfactory. (C)

The over-all average radial erosion rate calculated from pre- and post-firing throat dimensions was 1.91 mils per second. Post-firing examination of the nozzle and ballistic calculations based on the motor pressure trace suggest the following series of events likely took place in this test. (C)

A significant initial loss of coating occurred within the first 5 seconds or so, probably at the exit end of the insert. For a major portion of the firing, erosion proceeded by minor spallation and edge chipping at the exit end of the coating to yield an average erosion rate of about 1.2 mils per second. During this period the location of the throat plane apparently moved upstream. Finally more rapid erosion occurred near the end of the firing as a greater amount of the substrate graphite was exposed. In Figure 19 the estimated throat radii during this firing are shown as determined by a ballistic calculation from point to point along the motor pressure curve. It was indicated by this firing that the pyrolytic graphite coating was not likely to be tolerant of delamination flaws under service conditions so severe as used in this program. (C)

2. Subscale Firing No. 2

The insert tested in the second subscale firing had a wrap-around coating contour at the exit end, but it still contained a partial (C)


CONFIDENTIAL

Table VIII. Motor Test Data Summary


Program Test No.	A.R.C. Firing Designation	Insert Description		Firing Conditions			Performance Data		
		Substrate	Coating Thickness (mil at throat)	Duration (sec)	Max. Mtr. Pressure (psi)	Avg. Mtr. Pressure (psi)	Throat dia. before Test (inch)	Throat dia. after Test (inch)	Avg. Radial Erosion Rate (mil./sec)
SS-1	EPb-1	ATJ	58	55.9	795	564	1.105	1.287/1.351	1.91
SS-2	EPb-2	ATJ	66	83.0	807	452	1.090/1.097	1.485/1.510	2.43
SS-3	EPb-3	ATJ	23	34.8	714	618	1.136	1.173/1.176	0.55
SS-4	EPb-5	ATJ	54	64.9	812	590	1.111	1.330/1.365	1.82
SS-5	EPb-6	Fibrous	51	37.3	589	530	1.190	1.227/1.249	0.64
FS-1	EPb-4	ATJ	42	36.6	723	623	2.316	2.429/2.493	2.01
FS-2	EPb-7	580	47	31.5	702	644	2.304	2.342/2.358	0.73
FS-3	EPb-8	Fibrous	75	42.8	777	697	2.259	2.328/2.342	0.89
FS-4	EPb-9	Fibrous	99	63.5	867	708	2.242	2.393	1.19

CONFIDENTIAL

CONFIDENTIAL

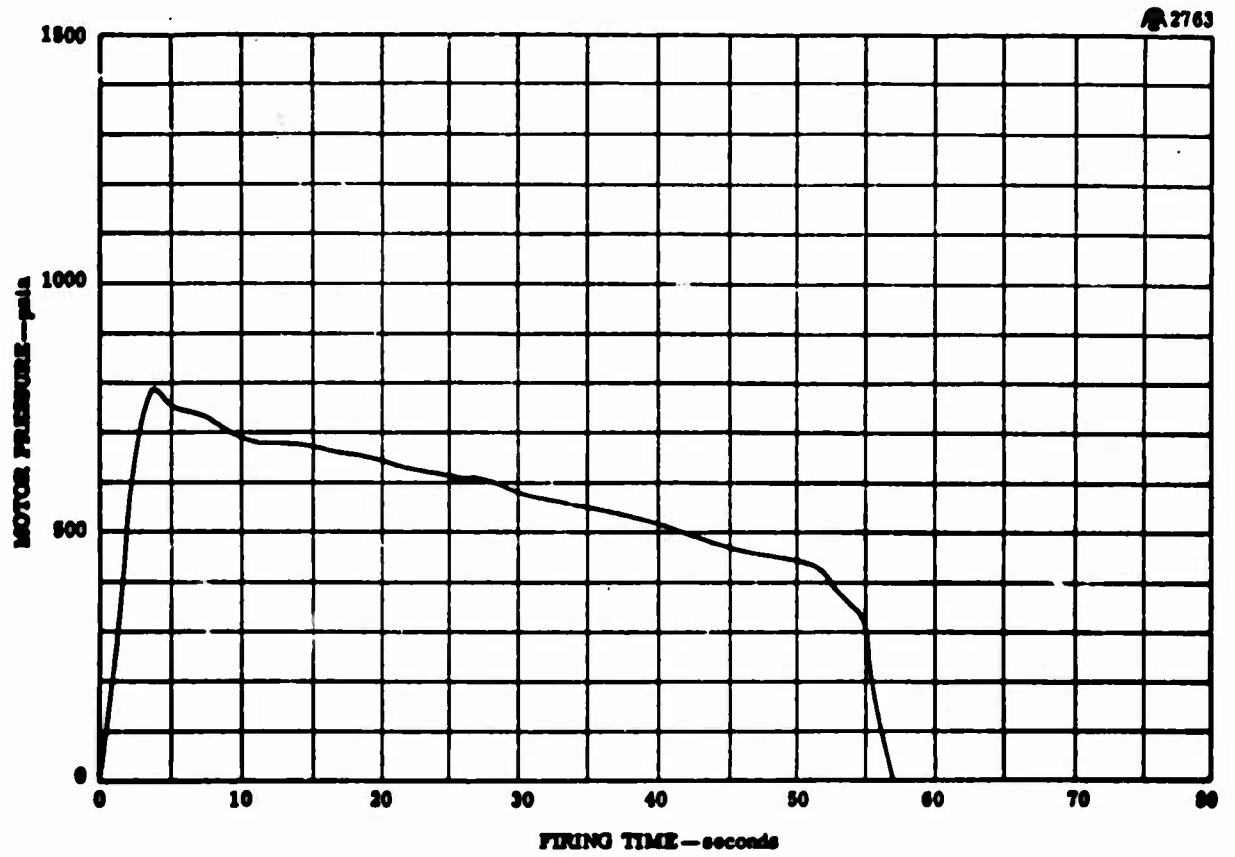

Subscale Firing No. 1

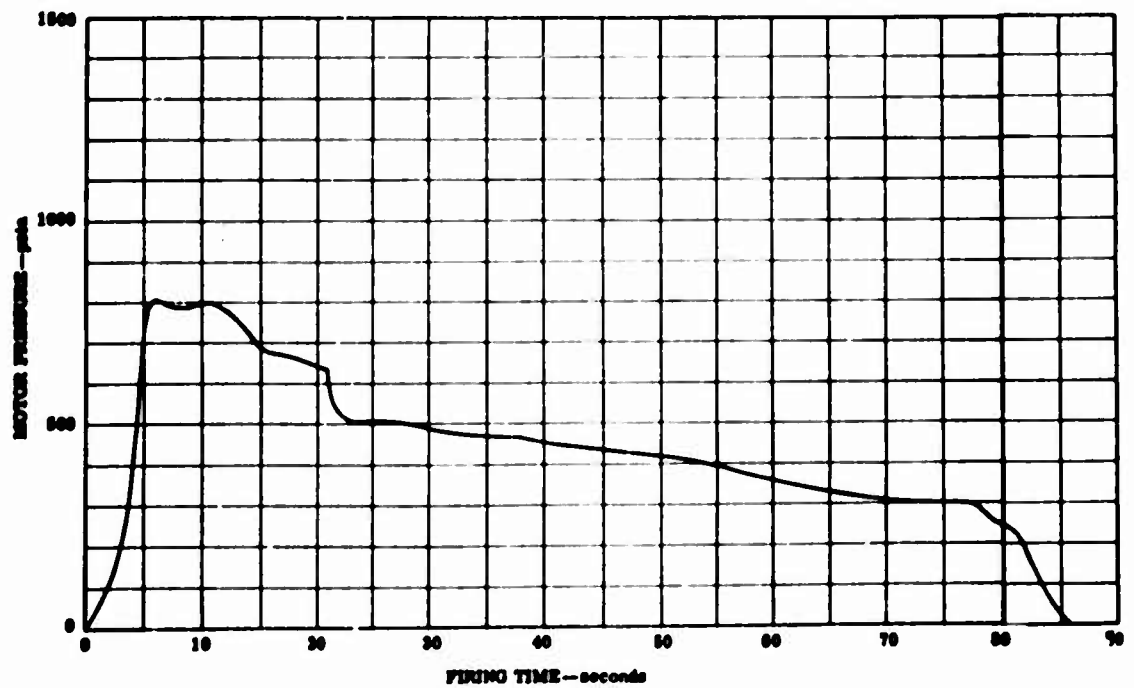

Subscale Firing No. 2

Figure 17. Motor Pressure Traces for Subscale Firings No. 1 and No. 2.

CONFIDENTIAL



Figure 18.. Axial View from Entrance End of Nozzle After Subscale Firing No. 1.

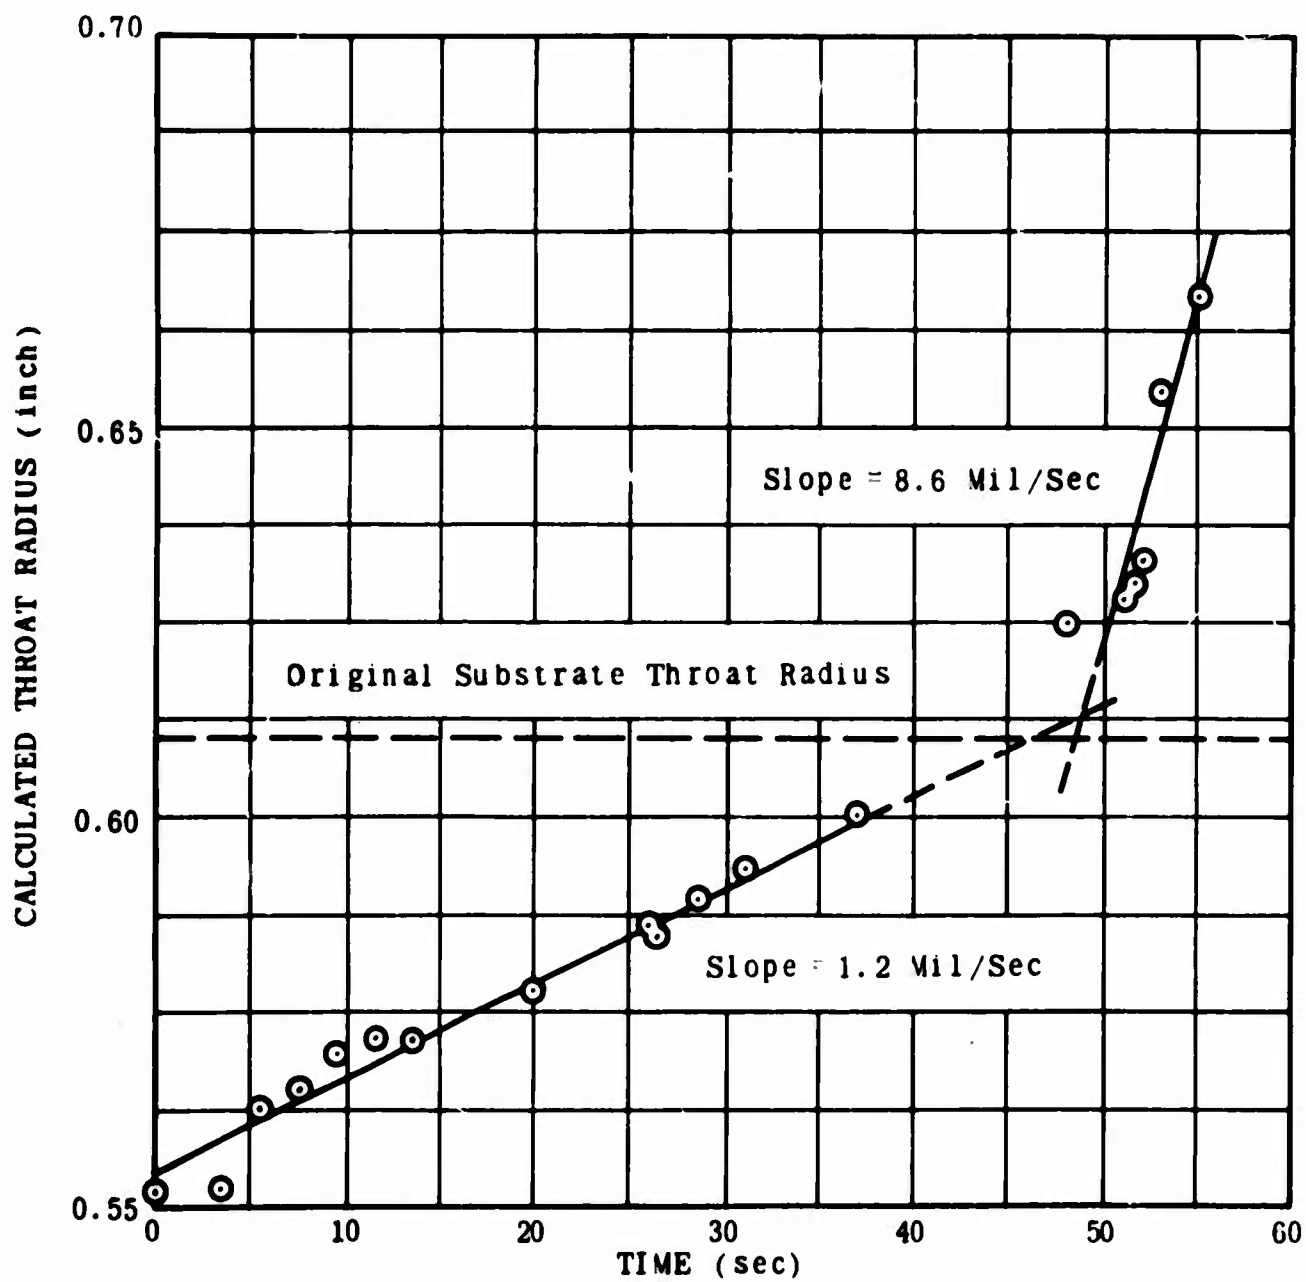


Figure 19. Calculated Throat Radii During Subscale Firing No. 1.

CONFIDENTIAL

AFRPL-TR-65-57


delamination flaw at the entrance end. The performance of this insert was poor and reinforced the belief that coatings are not tolerant of delamination flaws under severe service conditions. The pressure-time trace for this firing (Figure 17) shows clear evidence of the loss of sections of the coating during test. The total firing duration was 83 seconds and the coating was completely removed during test. The average radial erosion rate calculated from pre- and post-test measurements was 2.43 mils per second which clearly indicates the combined erosion of the coating and later the substrate. The relatively smooth pressure regression with the exception of the sudden pressure losses associated with coating spallation suggests that the coating eroded progressively from the downstream edge towards the entrance and provided some protection for the substrate during much of the firing period. (C)

3. Subscale Firing No. 3


The third subscale firing was the first test of a pyrolytic graphite coated insert which showed no visible cracks upon microscopic examination of both ends of the insert. The average erosion rate of 0.55 mil per second at an average motor pressure of 618 psi demonstrated the basic serviceability of a pyrolytic graphite coating when the coating integrity is maintained. The coating thickness on the insert tested was only 23 mils at the throat so that the firing duration was reduced to 34.8 seconds. The motor pressure trace shown in Figure 20 reflects the excellent performance of this nozzle. (C)

A most interesting and unique result of the firing test on the coating was observed in post-firing microscopic examination. The integrity of the coating was in no way decreased by the firing, but clear evidence of some plastic deformation of the pyrolytic graphite coating was found. This evidence for deformation is shown in two views of the post-firing microstructure in Figure 21. Markings in the coating resembling slip bands were found at numerous points in the coating. The lower view in Figure 21 includes a void area generated in the substrate beneath the coating which appears to have altered the point at which the two deformation bands intersect probably due to the reduced local stiffness of the substrate. The most significant conclusion to be drawn from these photomicrographs is that a pyrolytic graphite coating appears to be an excellent candidate for restart nozzle service. Further evidence is shown later to reinforce the conclusion that motor firing conditions do not degrade the remaining coating quality. The evidence of plastic deformation without cracking suggests that some relief may occur which could improve the stress distribution during recycle duty. (U)

CONFIDENTIAL

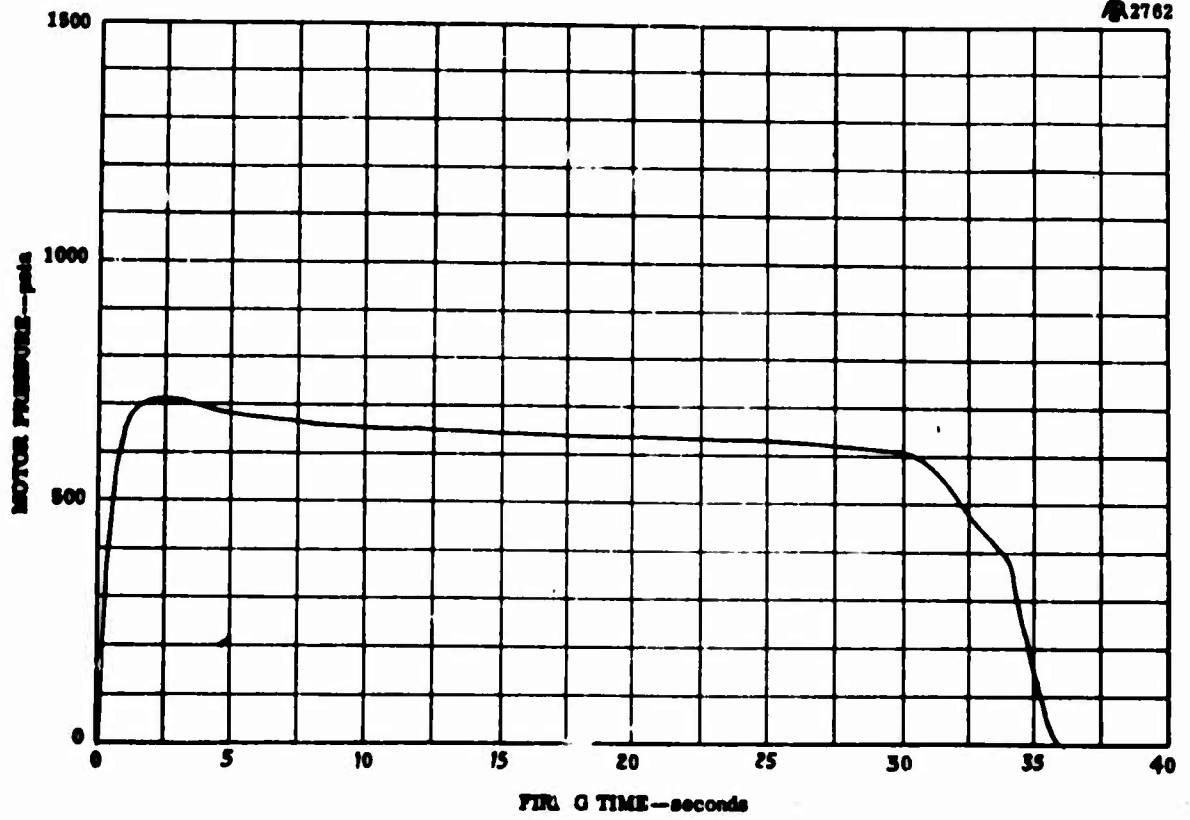

Subscale Firing No. 3

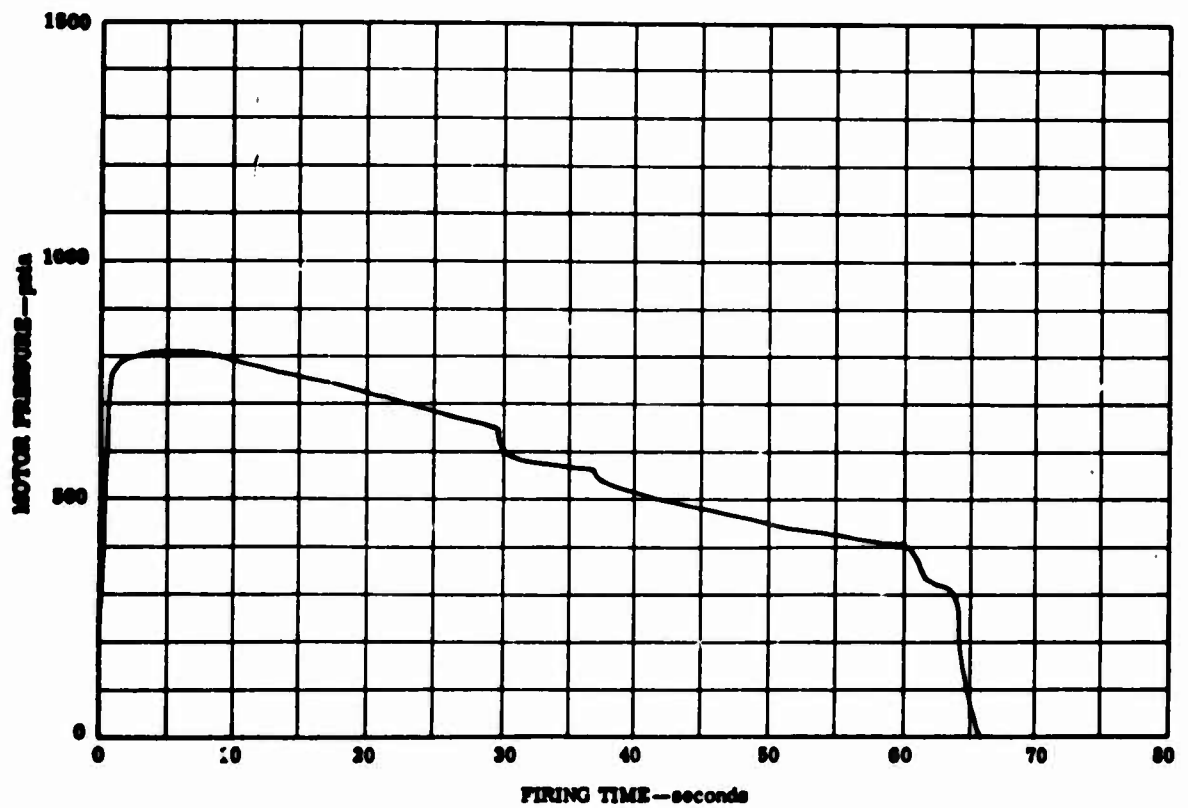

Subscale Firing No. 4

Figure 20. Motor Pressure Traces for Subscale Firings No. 3 and No. 4.

CONFIDENTIAL

AFRPL-TR-65-57



a. Exit (X150)



b. Exit (X150). Note Void in Substrate.

2750

Figure 21. Microstructure of Pyrolytic Graphite Showing Evidence of Deformation After Subscale Firing Number 3.

4. Subscale Firing No. 4

This firing was carried out to demonstrate the erosion resistance of a thicker coating in substantiation of subscale firing No. 3. The insert tested consisted of a 54-mil thick coating of pyrolytic graphite on a molded graphite substrate. The performance of this insert was disappointing. Discrete losses of coating occurred first at about 29 seconds and again at 37 seconds. The motor pressure trace for this firing is shown in Figure 20. The duration of this firing was 64.9 seconds and the average motor pressure was 590 psi, reduced to this level from an initial maximum motor pressure of 812 psi by an erosion rate averaging 1.82 mils per second. (C)

Although ballistic calculations indicate that the erosion rate of the coating prior to the first discrete loss of coating at about 29 seconds was only 0.7 to 0.8 mil per second, the failure of the coating was serious, but it was the only instance of loss of a crack-free coating in the entire program. It must be concluded that in this insert the cumulative effect of residual stresses from deposition and the thermal stresses generated during the firing caused progressive coating failure. Although this behavior may have resulted from an undetected flaw in this particular insert, time did not permit further study of the optimization of coatings on subscale molded graphite inserts. Instead, a more immediate means of reducing the stress effects was sought through the choice of another substrate material. The extent to which stress control can be achieved through the use of a low modulus substrate is discussed in the section on stress analysis, and the success of this approach was demonstrated in the next subscale firing. (C)

5. Subscale Firing No. 5

The coated insert tested in this firing consisted of a 51-mil thick pyrolytic graphite coating on a low modulus fibrous graphite substrate. During the 37 second duration at an average motor pressure of 530 psi, the coating erosion rate averaged 0.64 mil per second. The pressure trace is reproduced in Figure 22. This firing was significant for two reasons. It again demonstrated that a coating without observable flaws could give good performance under severe nozzle conditions. Second, it illustrated that the low modulus fibrous graphite could be successfully utilized as a substrate and survive not only residual stresses involved in deposition, but also the rigors of motor firing. Demonstration of this second fact was particularly important prior to the use of such a fibrous graphite substrate for fullscale firing tests. A photograph of the nozzle assembly after test shown in Figure 23 confirms the good condition of the nozzle. (C)


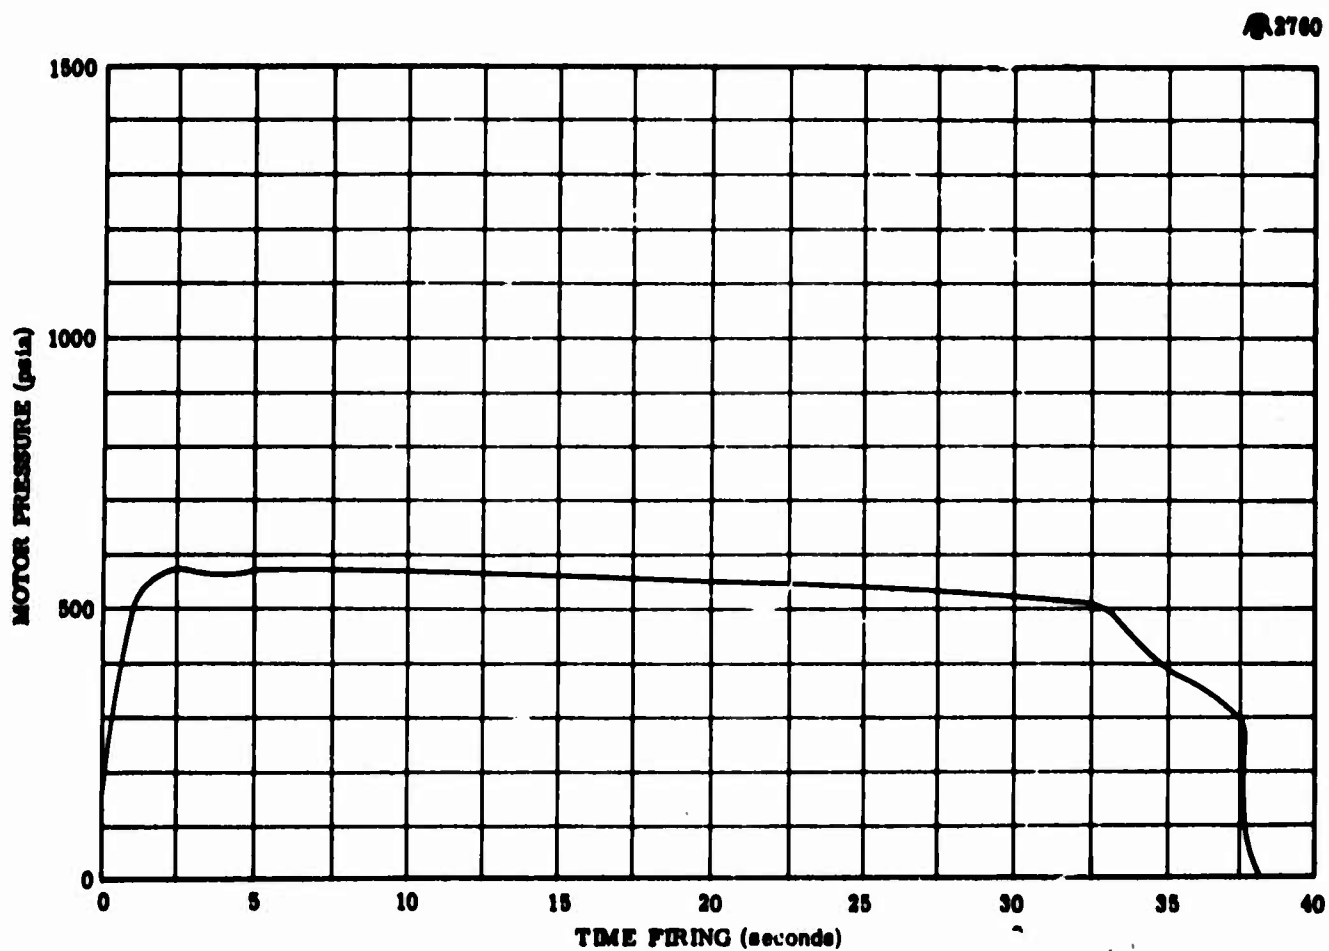


Figure 22. Motor Pressure Trace for Subscale Firing No. 5.

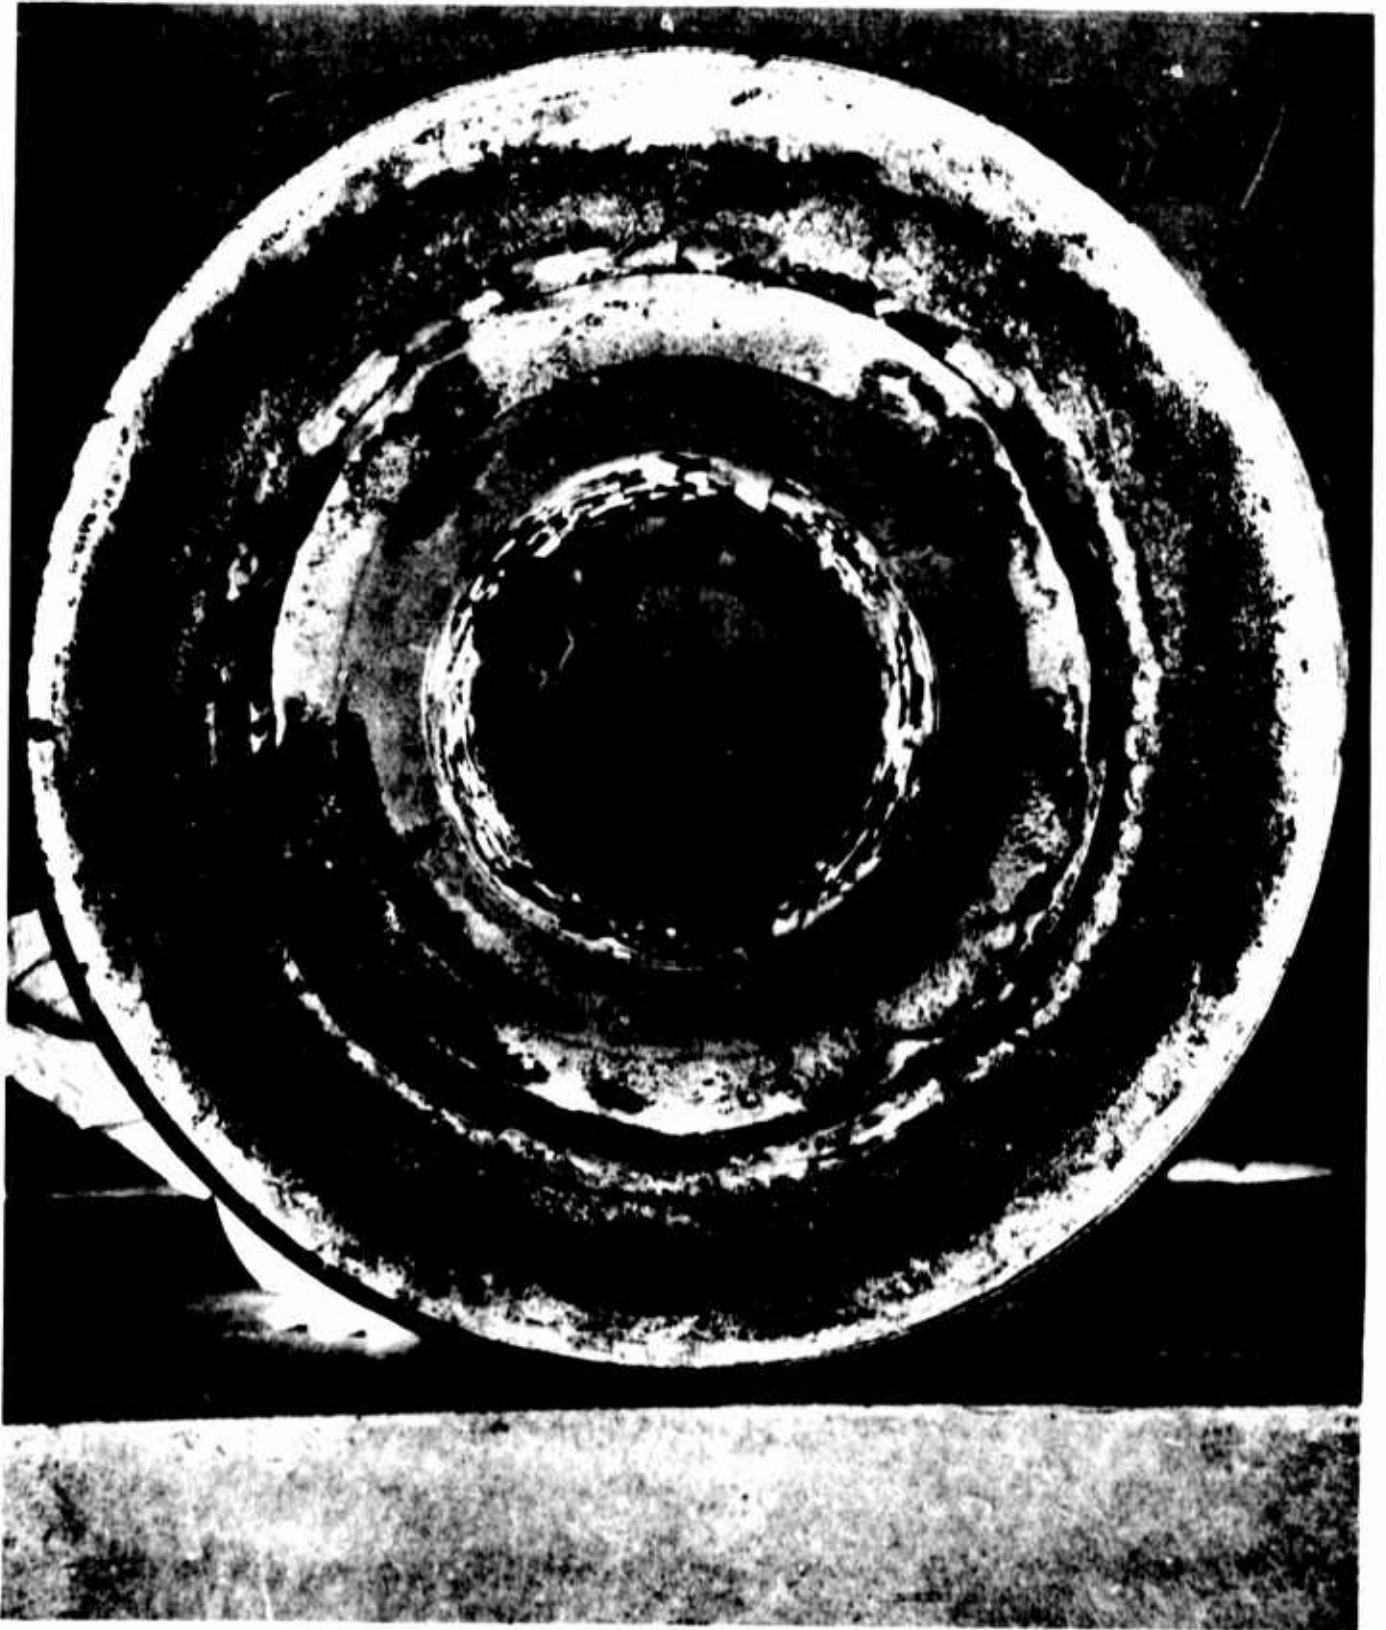

AR 2738

Figure 23. Axial View from Entrance End of Nozzle After Subscale Firing Number 5.

CONFIDENTIAL

AFRPL-TR-65-57

6. Implication of Subscale Test Results

The subscale firings in this program were intended to define problem areas in pyrolytic graphite coatings and to insure the successful demonstration of the feasibility of such coatings for fullscale nozzles. From the results of the five subscale firings, the following conclusions were drawn. The tolerance of pyrolytic graphite coatings for delamination flaws is low. However, it was also indicated that coatings free from visible flaws in microscopic examination could yield excellent nozzle performance for coatings on both molded substrates and low modulus fibrous substrates. The losses from the 54-mil thick coating tested in the fourth subscale firing, reinforces the belief that coating integrity is related to the deposition residual stresses. Although no flaws were visible in this insert, it is apparent that the coating was near the upper limit for flaw-free deposition and it is likely that the built-in stresses led to failure when firing stresses were superimposed on the insert. (C)

C. FULLSCALE MOTOR FIRINGS

Four fullscale firing tests using a 2.3-inch nozzle diameter in a 4600 pounds thrust motor were carried out in this program. The fullscale nozzle design which is shown in Figure 24 was similar to that used for the subscale unit. The goal of these firings was to demonstrate the performance capability of pyrolytic graphite coatings in nozzles of a usable and practical size. Each of the fullscale firings is discussed separately in the following sections and the implications of these results are indicated. (U)

1. Fullscale Firing No. 1

The fullscale firing program overlapped the subscale program in the same way that the deposition work for the two size ranges overlapped. This overlap was used to assure that results derived for subscale nozzles would be applicable to fullscale systems. The inserts selected for the first fullscale firing consisted of a 42-mil thick coating on molded graphite and contained a visible microscopic separation of the coating from the substrate at the exit end. The nature of the flaw in this insert was quite different from those found in early subscale units. A test of the effect of such a flaw on fullscale nozzle performance was deemed desirable. This firing was made prior to the point in the deposition study when flaw-free fullscale coatings were prepared. (U)

The performance of this fullscale insert with a known delamination flaw was quite similar to the results obtained previously in the subscale test with an insert with a flaw at the exit end. The over-all erosion rate, based on before-and after-test diameter measurements was 2.01 mils per second. The motor pressure trace shown in Figure 25 indicated a steady but excessive erosion pattern. The firing duration (C)

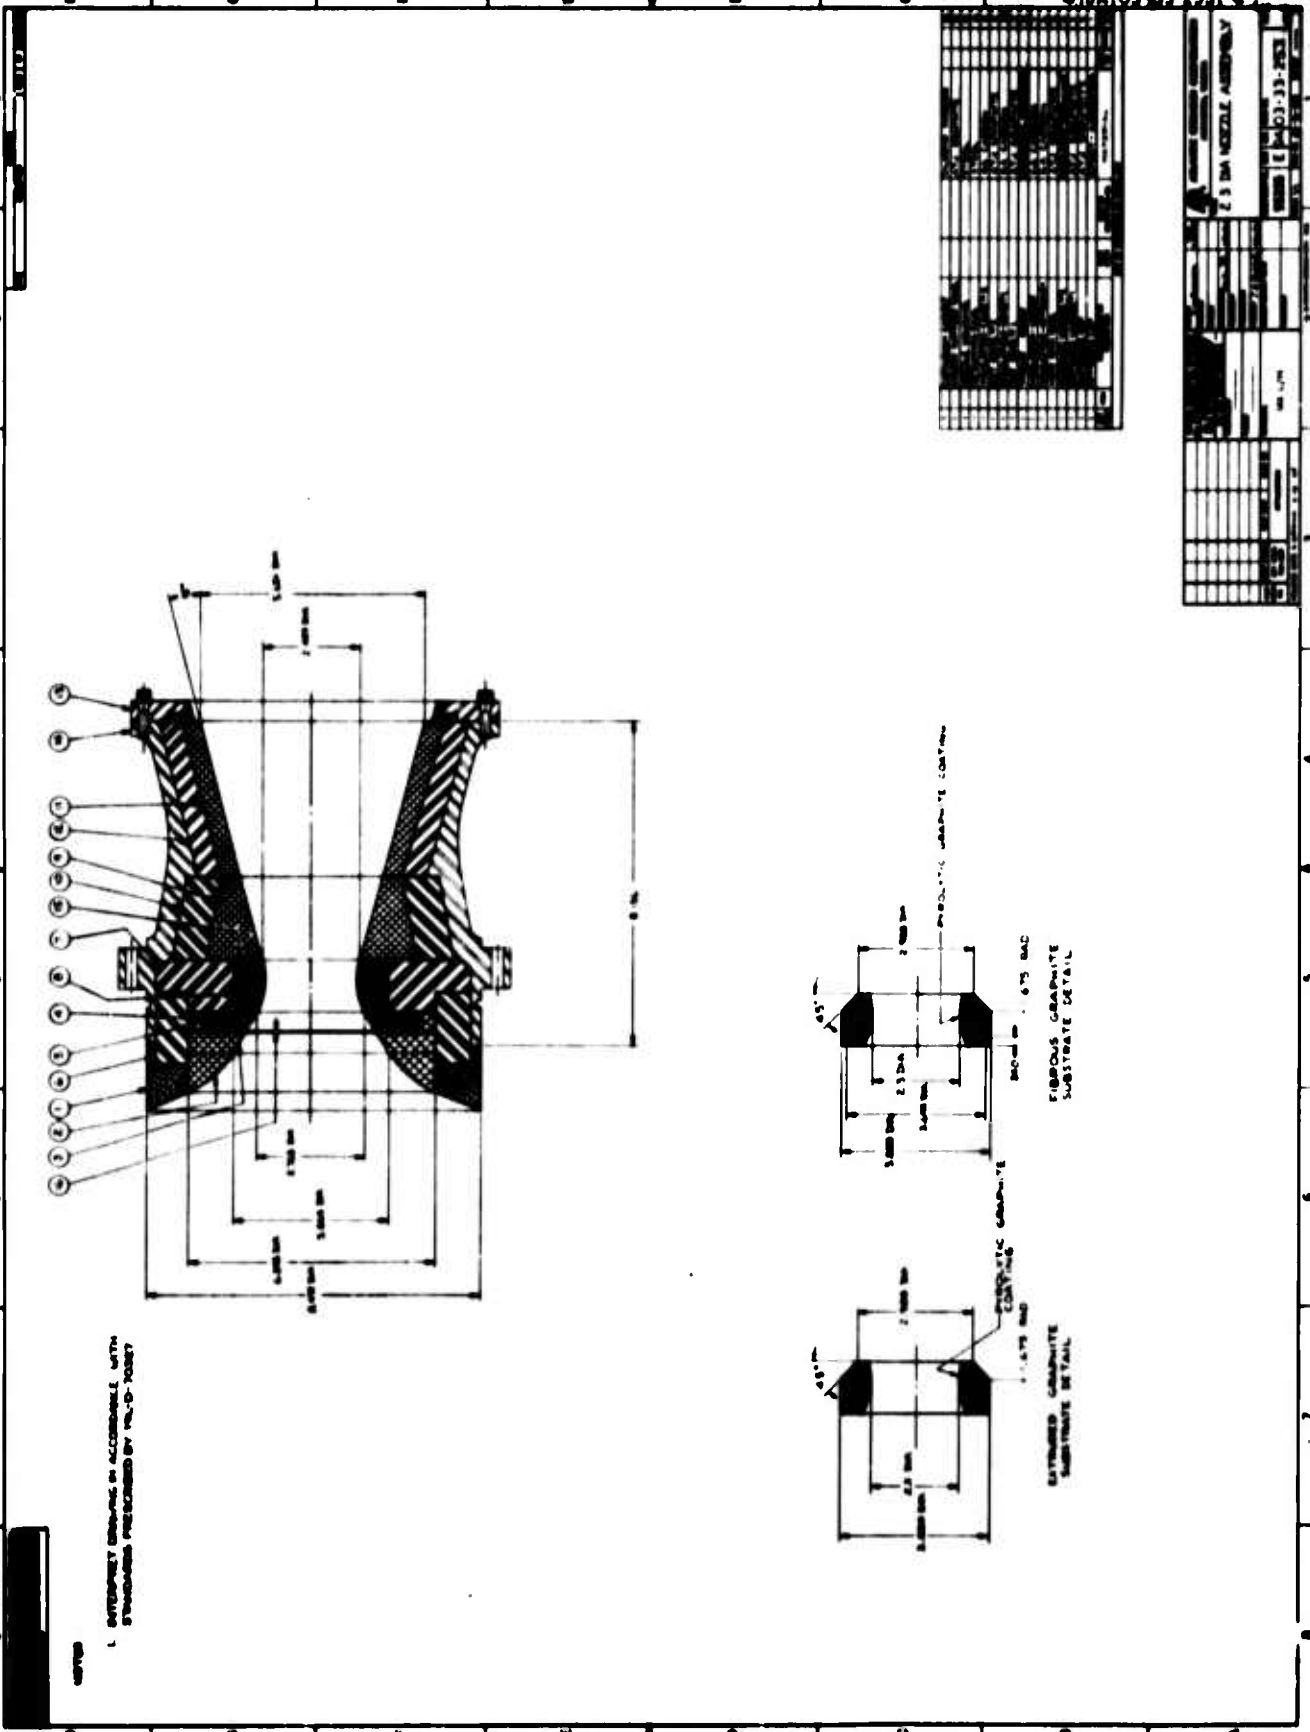
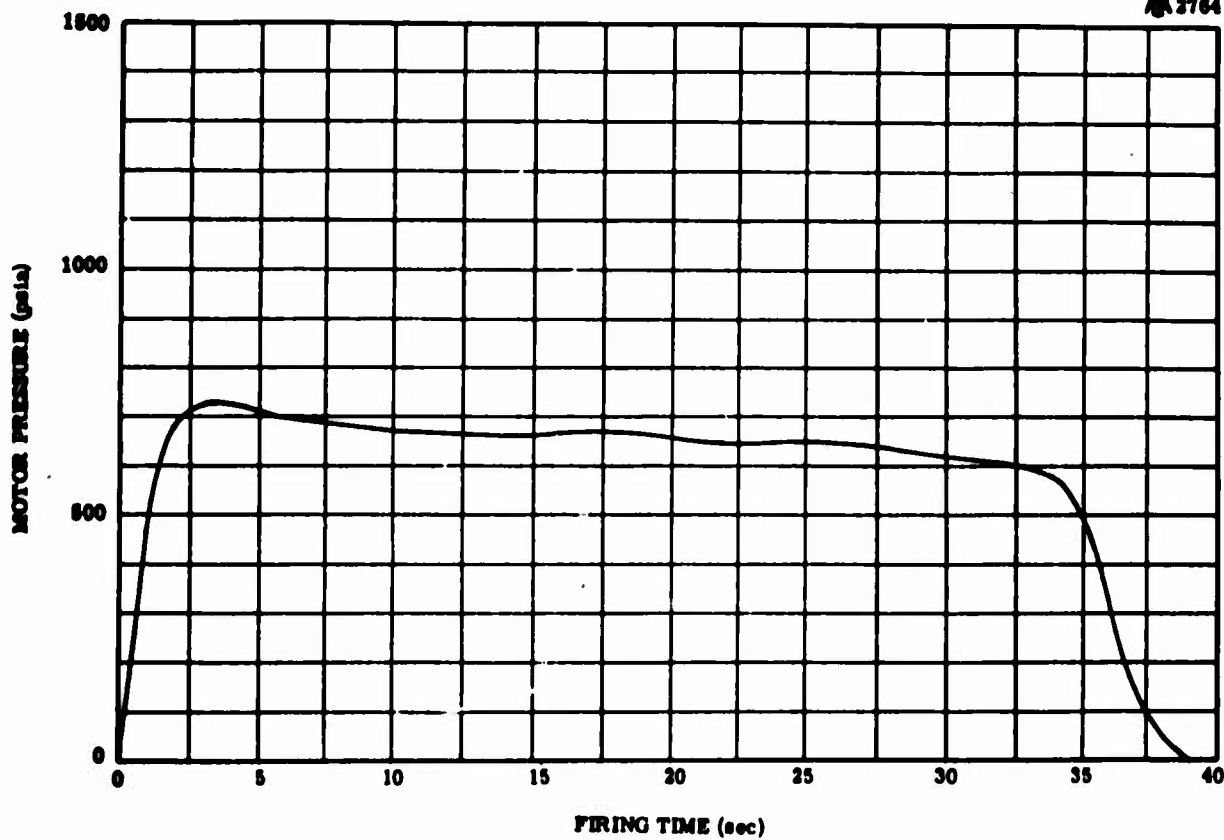
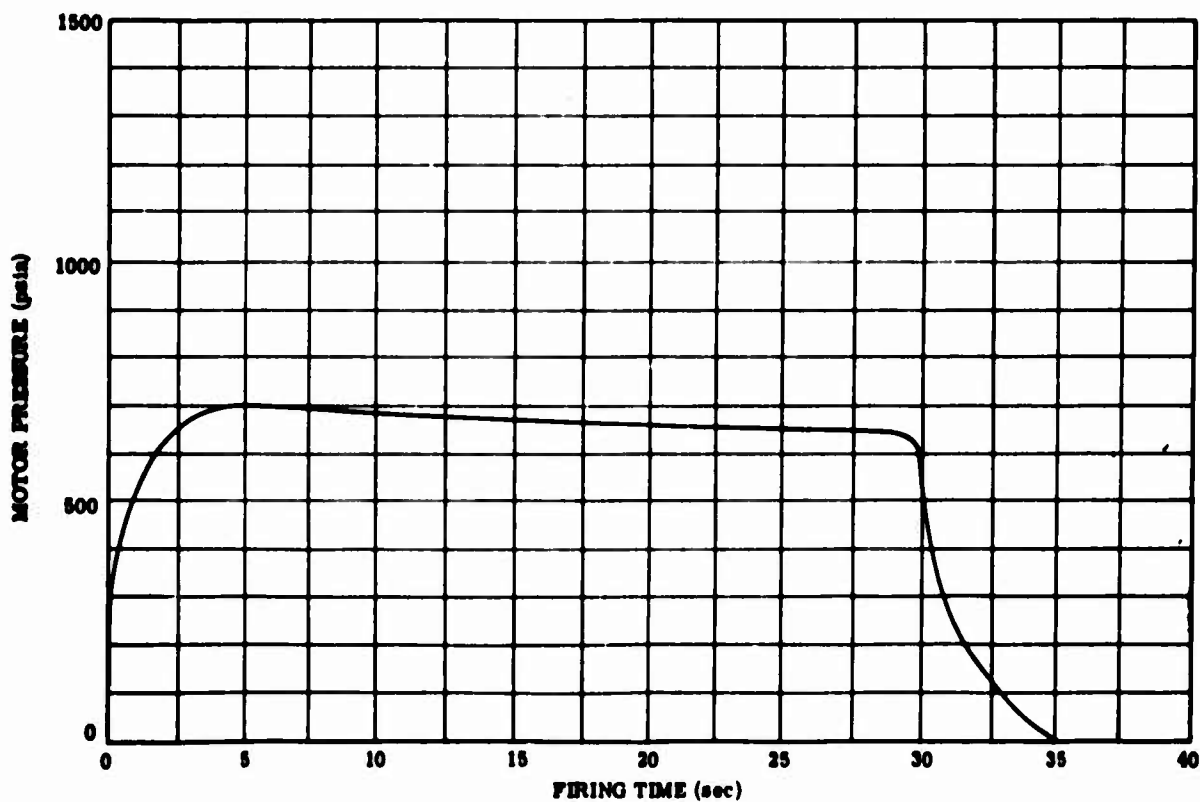


Figure 24. Fullscale Nozzle Assembly Drawing.

CONFIDENTIAL

3764

**Fullscale Firing No. 1****Fullscale Firing No. 2****Figure 25. Motor Pressure Traces for Fullscale Firings No. 1 and No. 2.****CONFIDENTIAL**

CONFIDENTIAL

was 36.6 seconds at an average motor pressure of 623 psi. A summary of motor test data for the fullscale firings is included in Table VIII. (C)

The consistent failure of coated inserts with known flaws to provide suitable performance suggested that flaw-free inserts were a must to achieve optimum performance. (U)

2. Fullscale Firing No. 2

Prior to fullscale Firing No. 2, successful deposition of a flaw-free coating on a Speer Carbon extruded graphite substrate (Grade 580) was achieved. The second fullscale test utilized such an insert with a 47-mil thick coating. This firing was completely successful. The insert showed an average erosion rate of 0.73 mil per second and an average motor pressure 644 psi for a firing duration of 31.5 seconds. The motor pressure trace for this test is included in Figure 25. After test the coating was intact and in good condition with approximately one-half of the original coating thickness remaining. (C)

Further evidence of the excellent condition of the coating remaining on the insert after this test was found by examining the microstructure of the coating. This microstructure, shown in Figure 26, is in every way similar to that of the insert prior to test and shows no indication of damage or cracking. (U)

3. Fullscale Firing No. 3

The deposition work indicated that a low modulus, fibrous graphite was an interesting alternative to the Grade 580 extruded graphite substrate. The final subscale firing had indicated that a pyrolytic graphite coating on a fibrous graphite substrate was suitable for motor service. To confirm this performance at the fullscale, a coating 75 mils thick deposited on a fibrous graphite substrate was tested in the third fullscale firing. The nozzle gave good performance. An average erosion rate of 0.88 mil per second was measured for an average motor pressure of 697 psi and a firing duration of 42.8 seconds. The motor pressure trace for this firing is shown in Figure 27. (C)

After test, the coating was intact and in generally good condition. Approximately one-half of the original thickness of the coating remained. Two views of the entrance end of the nozzle after test are shown in Figures 28 and 29. These figures indicate the good condition of the entire assembly. The microstructure of the coating after firing shown in Figure 30 again demonstrates that no discernable change occurs in the coating because of the motor exposure. (U)

CONFIDENTIAL



a. Entrance (X150)



b. Exit (X150)

2749

**Figure 26. Microstructure of Pyrolytic Graphite Coating
After Fullscale Firing Number 2.**


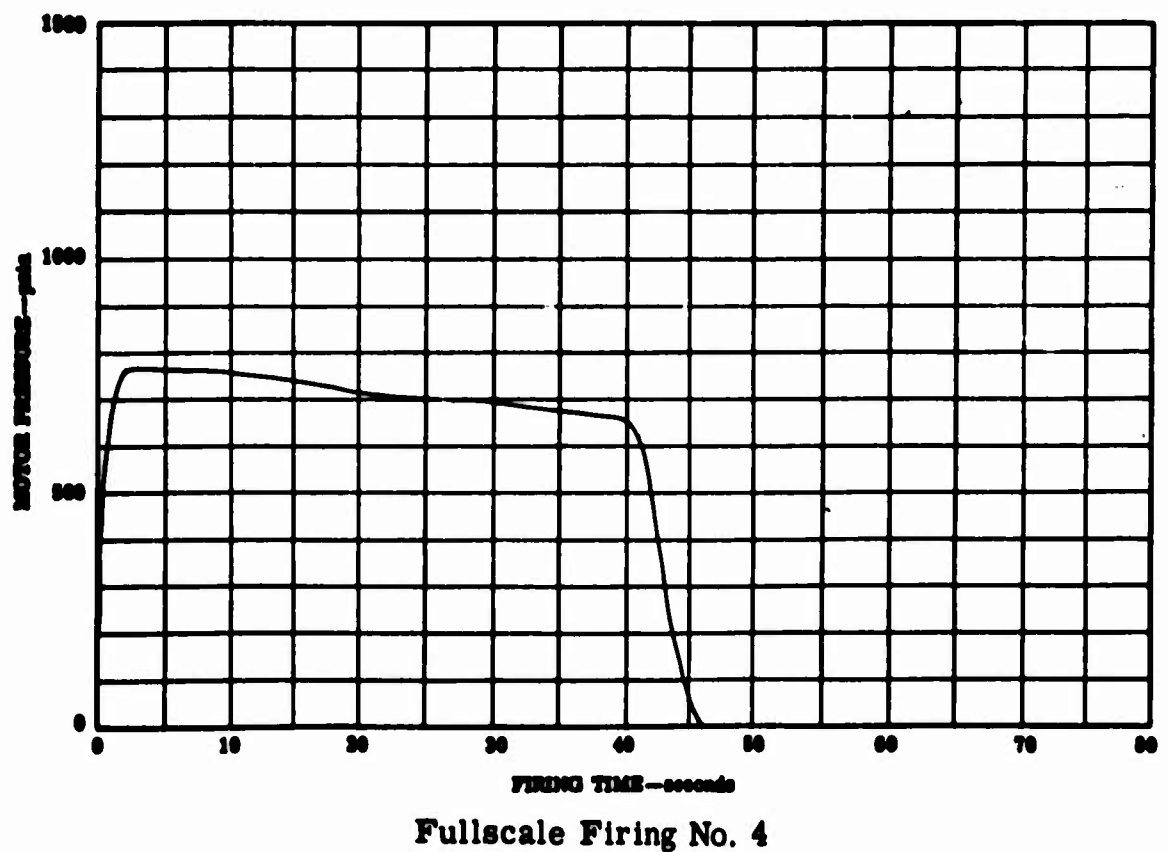


Figure 27. Motor Pressure Traces for Fullscale Firings No. 3 and No. 4.



2737


Figure 28. Axial View from Entrance End of Nozzle
After Fullscale Firing No. 3.

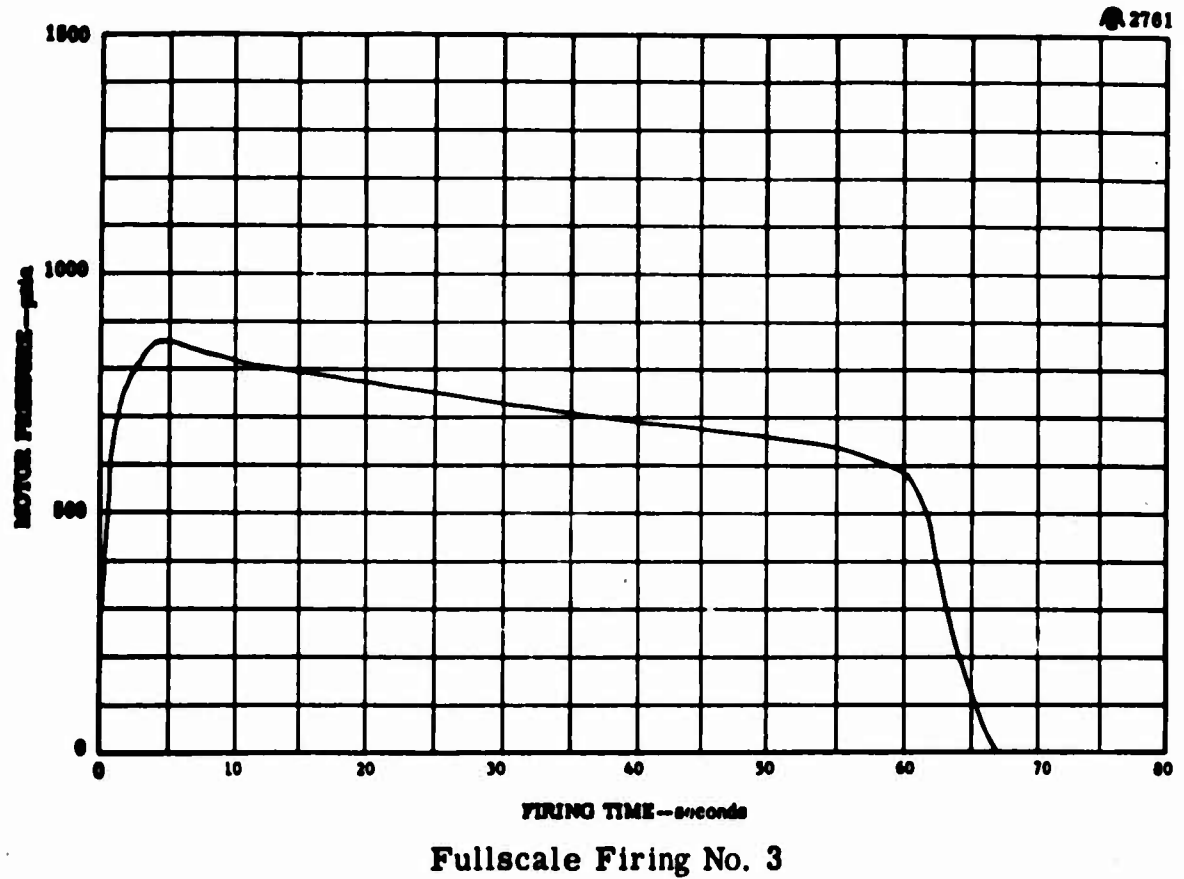

2736

Figure 29. Oblique View from Entrance End of Nozzle
After Fullscale Firing No. 3.

AFRPL-TR-65-57

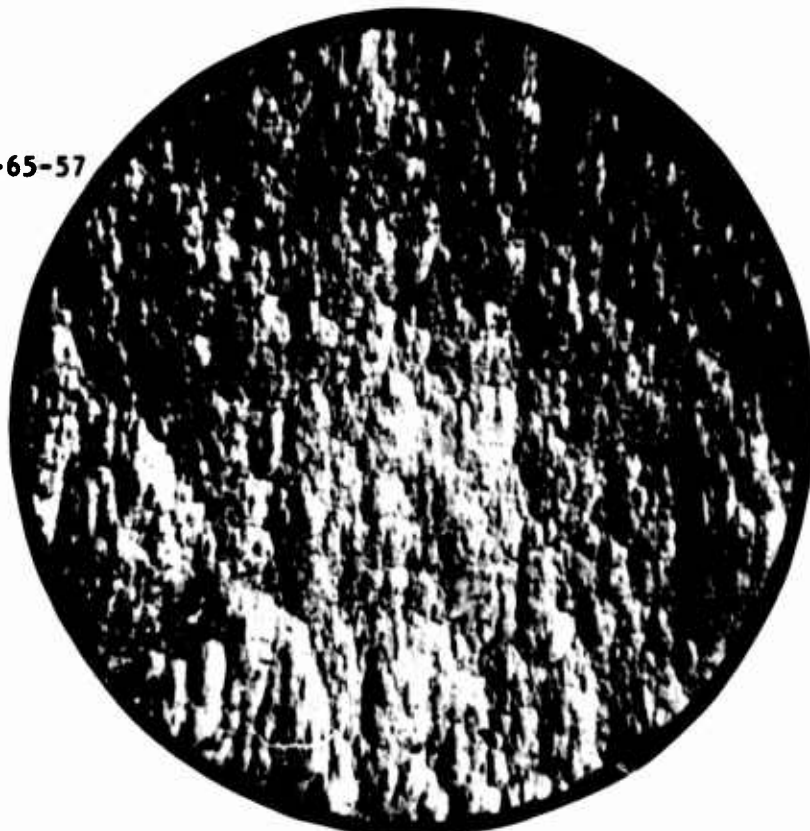

a. Entrance (X150)



b. Exit (X150)

2748

**Figure 30. Microstructure of Pyrolytic Graphite Coating
After Fullscale Firing Number 3.**

AFRPL-TR-65-57

4. Fullscale Firing No. 4

In selecting an insert for this final fullscale motor firing, the alternative of using an extruded graphite or a fibrous graphite substrate was available. As discussed earlier in the deposition study, coatings of sufficient thickness were not successfully prepared on the extruded substrate. Time did not permit the further pursuit of the deposition study, so an insert consisting of a 100-mil coating of pyrolytic graphite on a fibrous graphite substrate was selected for test. The goal of this firing was to demonstrate a full duration capability of more than 60 seconds for a pyrolytic graphite coated nozzle under the severe motor conditions selected for this program. This goal was achieved in fullscale Firing No. 4 which had a firing duration of 63.5 seconds and an average motor pressure of 708 psi. The motor pressure trace for this test is shown in Figure 27. (U)

Although this firing represented a successful full duration test, the success was qualified by two factors. First, although the motor pressure trace was smooth, a local gouge occurred in the nozzle coincident with motor tailoff. This gouge, which because of the soft and non-erosion resistant nature of the fibrous substrate is sizeable, is seen in the two views of the post fired nozzle in Figures 31 and 32. Second, the average erosion rate calculated from post-firing measurements in areas away from the local gouge indicated a higher than normal erosion rate of 1.19 mils per second. Both of these qualifications on the success of this firing are believed to have resulted from the non-uniform quality of the coating. As indicated in the deposition study section, the coating tested in this firing had more than normal roughness associated with nodules in the coating. To avoid effects associated with turbulence due to surface roughness, the surface of the coating was polished prior to test. However, this smoothing operation could not eliminate the effect of local flaws in nodules on the coating erosion. It is likely that enhanced erosion occurred in the regions where local flaws in the nodules became exposed to the surface. Although the local flaws associated with nodules in the coating probably produced microspallation of the coating locally, the microstructure shown in Figure 33 indicates that this type of flaw does not lead to catastrophic changes in the coating integrity. In Figure 33 the presence of submerged local flaws in the coating remaining after tests indicates this conclusion to be valid. (C)

5. Implications of Fullscale Test Results

The complete loss of the coating of the first fullscale firing again indicates that coatings with known delamination cracks are not suited for severe nozzle applications. The successful completion of the remaining fullscale tests with nozzles that did not contain delamination cracks demonstrated the feasibility of pyrolytic graphite coated nozzles for fullscale applications. Optimization of coatings on fullscale inserts was not within the scope of this program, but the successful performance of three fullscale coated inserts does point to the inherent advantage of this light-weight nozzle system. (U)


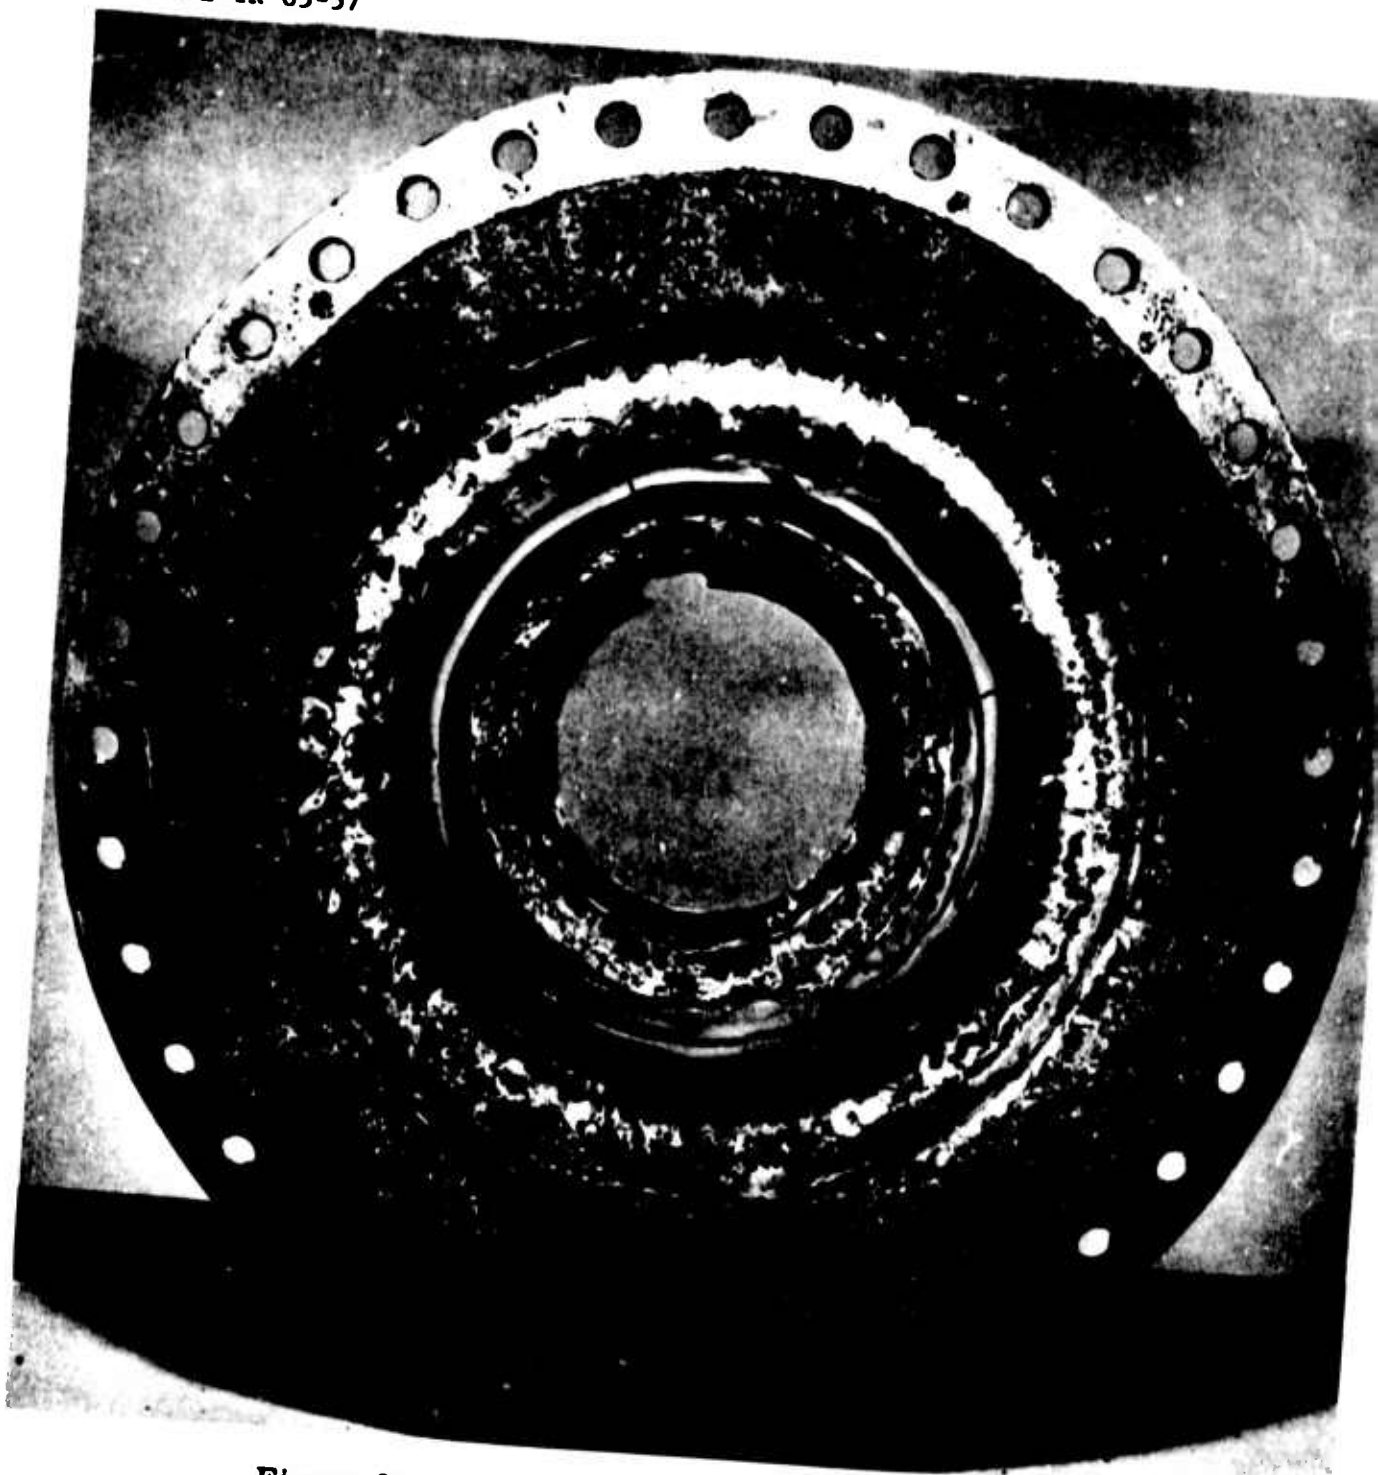


Figure 31. Axial View from Entrance End of Nozzle
After Fullscale Firing No. 4.

2734

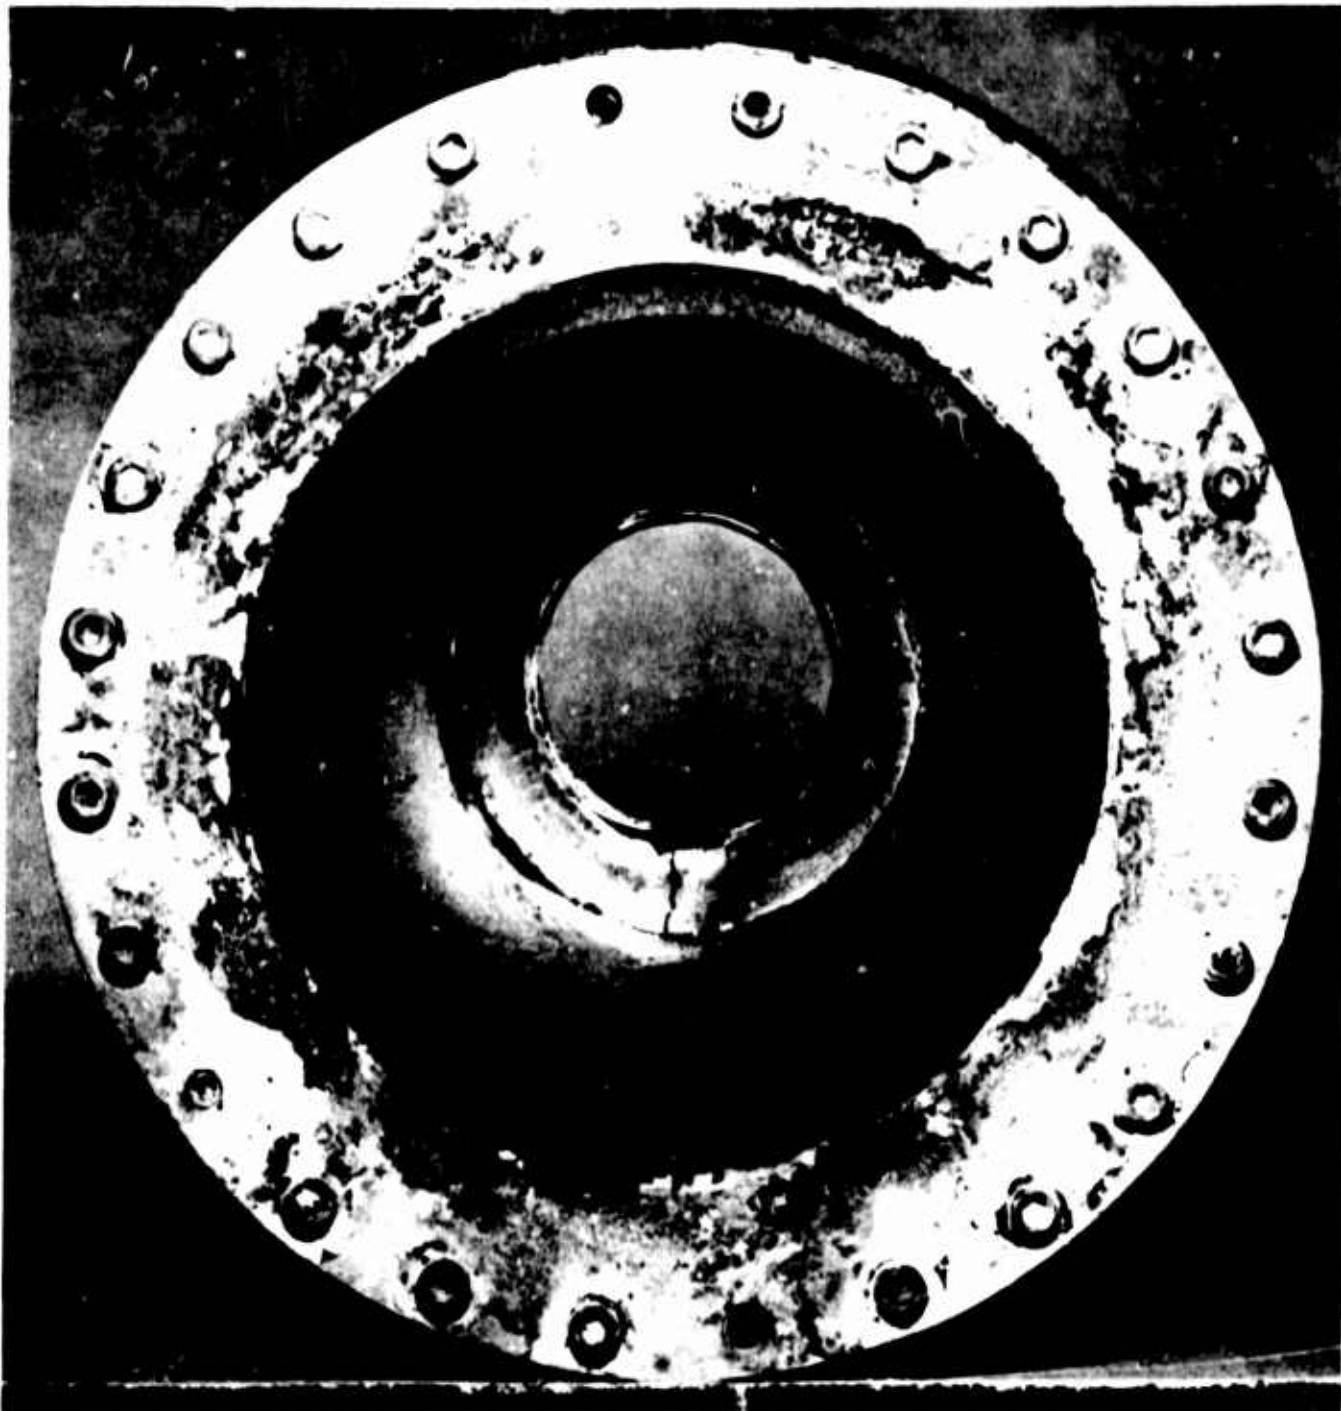

2735

Figure 32. Axial View from Exit End of Nozzle
After Fullscale Firing No. 4.

AFRPL-TR-65-57



a. Exit (X150)



b. Local Flaws in Nodule (X150)

2747

Figure 33. Microstructure of Pyrolytic Graphite Coating After Fullscale Firing Number 4.

List of References

1. Improvement of the Usefulness of Pyrolytic Graphite in Rocket Motor Applications, Batchelor, J. D., Ford, E. F., and Olcott, E. L., Atlantic Research Corporation, February 1963, Contract No. DA-36-034-ORD-3279Z, Final Technical Summary Report.
2. Research and Development in Solid-Propellant Rocketry and Related Fields, Atlantic Research Corporation, April 1960 to October 1961, Contract No. NOrd 15536, Quarterly Progress Reports 40 - 46.
3. Special Projects Materials Program, Atlantic Research Corporation, April 1963, Contract No. NOW 62-0511, Final Report.
4. Thermal Stresses in Pyrolytic Graphite, Levy, S., Presented at AIAA Launch and Space Vehicles Shell Structures Conference, Palm Springs, California, April 1963.
5. A Note on the Structure-Property Relationships for Pyrolytic Graphite, Coffin, L. F. Jr., Presented at AIAA Launch and Space Vehicle Shell Structures Conference, Palm Springs, California, April 1963.
6. Final Report on Work Statement No. 87, Residual Stress Studies, Smith, W. H., Clark, T. J., and Larsen, R. J., September 1961, General Electric Report No. PI-WS-0232.
7. Pyrolytic Graphite Engineering Handbook, General Electric Company, July 1963.
8. Pyrolytic Graphite Handbook, Super-Temp Corporation, 1963.
9. Industrial Graphite Handbook, National Carbon Company.
10. Graphite Handbook, Speer Carbon Company, 1964.
11. Physical Properties of Some Newly Developed Graphite Grades, Dull, R. B., May 1964, WADD TR61-72, Vol. XXVI.

APPENDIX A

**Calculated Temperatures in Various Nozzle Designs
Utilizing Pyrolytic Graphite Coatings**

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILMED.

AFRPL-TR-65-57

Case A-1

Throat Location: 1.100" diameter

Location Radius Node No.	Surface 0.550 1	Rear Graphite 1.180 11	Midpoint Carbon 1.580 14	Steel Average 2.200 17,18
<u>Time (sec)</u>	<u>Temperature °F</u>			
1	4470	140	70	70
2	4891	315	71	70
5	5330	845	92	70
10	5608	1513	206	70
20	5848	2365	568	79
30	5964	2899	935	106
40	6035	3270	1250	154
50	6083	3543	1510	216
60	6117	3751	1725	288

Case A-2

Throat Location: 1.100" diameter

Location Radius Node No.	Surface 0.550 1	Rear Graphite 1.440 13	Midpoint Carbon 1.730 15	Steel Average 2.200 17,18
<u>Time (sec)</u>	<u>Temperature °F</u>			
1	4430	84	70	70
2	4850	164	75	70
5	5283	533	150	70
10	5550	1114	398	78
20	5798	2004	959	143
30	5932	2654	1443	263
40	6021	3156	1846	413
50	6085	3557	2185	565

Case A-3

Throat Location: 1.100" diameter

Location	Surface	Near Rear PG	Rear Graphite	Midpoint Carbon	Steel Average
Radius	0.550	0.574	1.180	1.580	2.200
Node No.	1	5	14	17	20,21
<u>Time (sec)</u>	<u>Temperature, °F</u>				
1	5925	804	85	70	70
2	5959	1119	152	70	70
5	6006	1643	405	78	70
10	6054	2184	780	133	70
20	6113	2866	1350	332	74
30	6151	3326	1772	560	89
40	6178	3620	2041	776	116
50	6199	3858	2365	970	154
60	6215	4046	2582	1142	201

Case A-4

Throat Location: 1.100" diameter

Location	Surface	Near Rear PG	Rear Graphite	Midpoint Carbon	Steel Average
Radius	0.550	0.574	1.440	1.720	2.200
Node No.	1	5	16	18	20,21
<u>Time (sec)</u>	<u>Temperature. °F</u>				
1	5925	801	72	70	70
2	5958	1117	94	71	70
5	6004	1611	232	89	70
10	6045	2076	484	174	72
20	6096	2662	910	401	91
30	6129	3057	1247	615	132
40.4	6156	3360	1481	810	192
50.4	6175	3585	1756	974	259
59.4	6190	3749	1929	1107	325

Case A-5

Throat Location: 1.100" diameter

Location	Surface	Rear PG	Rear Graphite	Rear Carbon	Near Outside (in steel)
Radius	0.550	0.610	1.250	2.000	2.220
Node No.	1	6	14	20	21
<u>Time (sec)</u>	<u>Temperature, °F</u>				
.05	4720	70	70	70	70
.1	5130	70	70	70	70
.2	5450	73	70	70	70
.5	5782	100	70	70	70
1.0	5955	175	71	70	70
2.2	6081	348	95	70	70
5.2	6134	624	228	70	70
10.2	6152	939	456	70	70
20.2	6176	1406	826	72	71
30.2	6193	1758	1121	79	75
40.2	6207	2038	1364	92	84
50.2	6218	2268	1570	112	100
59.2	6227	2445	1732	135	119

Case A-6

Throat Location: 1.100" diameter

Location	Surface	Rear PG	Rear Graphite	Rear Carbon	Near Outside (in steel)
Radius	0.550	0.610	1.500	2.000	2.220
Node No.	1	6	16	20	21
<u>Time (sec)</u>	<u>Temperature, °F</u>				
.05	4720	70	70	70	70
.10	5130	70	70	70	70
.20	5450	73	70	70	70
.50	5782	100	70	70	70
1.0	5965	175	70	70	70
2.2	6081	348	77	70	70
5.2	6133	603	146	70	70
10.2	6149	857	297	71	70
20.2	6168	1230	565	78	73
30.2	6182	1522	790	97	86
40.2	6194	1762	983	125	108
50.2	6204	1966	1151	160	138
59.2	6212	2124	1285	197	170

Case B-1				
Throat Location: 2.300" diameter				
Location Radius Node No.	Surface 1.150 1	Near Rear Graphite 1.950 13	Near Rear Carbon 2.685 19	Near Outside (in steel) 3.0225 21
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	1880	70	70	70
.10	2410	70	70	70
.20	3000	70	70	70
.50	3778	72	70	70
1.0	4330	95	70	70
2.3	4901	247	70	70
5.3	5328	660	70	70
10.3	5602	1239	71	70
20.3	5839	2043	90	75
30.3	5957	2582	133	93
40.3	6029	2973	196	130
50.3	6079	3271	272	184
59.3	6112	3484	348	241

Case B-2

Throat Location: 2.300" diameter

Location Radius Node No.	Surface 1.150 1	Near Rear Graphite 2.185 15	Near Rear Carbon 2.685 19	Near Outside (in steel) 3.0225 21
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	1880	70	70	70
.10	2410	70	70	70
.20	3000	70	70	70
.50	3778	70	70	70
1.0	4330	74	70	70
2.3	4900	132	70	70
5.3	5321	370	71	70
10.3	5579	774	82	71
20.3	5797	1413	143	91
30.3	5909	1881	235	142
40.3	5981	2240	343	216
50.3	6032	2524	456	304
59.3	6066	2732	559	389

Case B-3

Throat Location: 2.300" diameter

Location	Surface	Rear PG	Rear Graphite	Rear Carbon	Near Outside (in steel)
Radius Node No.	1.150 1	1.195 6	2.000 12	2.750 20	3.000 21
<u>Time (sec)</u>	<u>Temperature, °F</u>				
.05	4550	70	70	70	70
.10	4980	71	70	70	70
.20	5330	81	70	70	70
.50	5692	155	70	70	70
1.0	5881	307	71	70	70
2.3	5995	592	96	70	70
5.3	6035	960	240	70	70
10.3	6065	1363	496	70	70
20.3	6105	1939	923	72	71
30.3	6135	2359	1266	80	76
40.5	6158	2690	1556	97	88
50.5	6175	2952	1797	122	108
60.5	6191	3169	2005	154	136
70.5	6203	3353	2187	193	170
80.5	6214	3511	2347	236	209
90.5	6224	3648	2489	282	252
100.5	6232	3767	2616	331	298
110.5	6239	3873	2730	383	346
120.5	6246	3967	2833	435	396
130.5	6252	4051	2927	487	447

Case B-4

Throat Location: 2.300" diameter

Location	Surface	Rear PG	Rear Graphite	Rear Carbon	Near Outside (in steel)
Radius Node No.	1.150 1	1.195 6	2.250 14	2.750 20	3.000 21
Time (sec)	Temperature, °F				
.05	4550	70	70	70	70
.10	4980	71	70	70	70
.20	5330	80	70	70	70
.50	5692	155	70	70	70
1.0	5881	307	70	70	70
2.3	5995	591	78	70	70
5.3	6035	949	158	70	70
10.3	6061	1309	336	71	70
20.3	6097	1810	663	80	75
30.3	6123	2181	939	103	90
31.3	6125	2213	965	106	93

Case B-7

Throat Location: 2.300" diameter

Location	Surface	Rear PG	Rear Graphite	Rear Carbon	Near Outside (in steel)
Radius Node No.	1.150 1	1.195 6	2.000 12	3.125 20	3.375 21
<u>Time (sec)</u>	<u>Temperature, °F</u>				
.05	4550	70	70	70	70
.10	4980	71	70	70	70
.20	5330	80	70	70	70
.50	5694	155	70	70	70
1.0	5882	307	71	70	70
2.2	5993	581	94	70	70
5.2	6035	954	237	70	70
10.2	6064	1359	493	70	70
20.2	6105	1937	921	70	70
30.2	6134	2357	1265	71	70
40.2	6157	2683	1550	73	72
50.2	6175	2947	1793	78	75
60.2	6190	3165	2002	85	81
70.2	6203	3350	2185	96	90
80.2	6214	3509	2348	111	102
90.2	6224	3647	2492	128	120
99.2	6231	3757	2610	147	135

Case C-1

Entrance Location: 1.840" diameter (1.100" throat)

Location	Surface	Rear PG	Rear Carbon	Near Outside (in steel)
Radius Node No.	0.920 1	1.750 5	2.250 9	2.5375 11
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	620	70	70	70
.10	850	70	70	70
.20	1150	71	70	70
.50	1650	92	70	70
1.0	2095	170	70	70
2.2	2692	417	70	70
5.2	3491	975	71	70
10.2	4207	1675	80	72
20.2	4925	2607	140	103
30.2	5299	3214	243	177
40.2	5528	3641	371	281
50.2	5683	3955	507	399
59.2	5783	4170	631	511

Case C-2

Entrance Location: 1.840" diameter (1.100" throat)

Location	Surface	Rear PG	Rear Carbon	Near Outside (in steel)
Radius	0.920	1.750	2.625	2.925
Node No.	1	5	10	12
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	620	70	70	70
.10	850	70	70	70
.20	1150	71	70	70
.50	1650	92	70	70
1.0	2095	171	70	70
2.2	2692	418	70	70
5.2	3492	979	70	70
10.2	4210	1681	70	70
20.2	4928	2613	74	71
30.2	5301	3222	89	80
40.2	5532	3655	118	101
50.2	5689	3979	160	135
59.2	5791	4206	209	175

Case D-1

Entrance Location: 3.540" diameter (2.300" throat)

Location	Surface	Rear PG	Rear Carbon	Near Outside (in steel)
Radius	1.770	2.625	3.250	3.5375
Node No.	1	6	12	14
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	670	70	70	70
.10	900	70	70	70
.20	1180	71	70	70
.50	1690	90	70	70
1.0	2181	175	70	70
2.2	2842	445	70	70
5.2	3703	1054	70	70
10.2	4442	1810	72	70
20.2	5148	2799	99	82
30.2	5500	3433	162	123
40.2	5712	3876	255	194
50.2	5852	4200	365	285
60.2	5950	4445	484	391
70.2	6022	4635	605	501
80.2	6077	4783	725	612
90.2	6118	4902	841	723
99.2	6148	4990	943	820

Case D-2

Entrance Location: 3.540" diameter (2.300" throat)

Location	Surface	Rear PG	Rear Carbon	Near Outside (in steel)
Radius	1.770	2.625	3.625	3.925
Node No.	1	6	13	15
<u>Time (sec)</u>	<u>Temperature, °F</u>			
.05	680	70	70	70
.10	900	70	70	70
.20	1180	71	70	70
.50	1690	90	70	70
1.0	2181	176	70	70
2.2	2842	446	70	70
5.2	3704	1059	70	70
10.2	4444	1817	70	70
20.3	5156	2815	71	70
30.3	5506	3446	78	74
40.3	5716	3880	95	85
50.3	5855	4212	124	107
60.3	5954	4461	164	139
70.3	6027	4655	214	182
77.4	6067	4768	254	216

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILMED.

AFRPL-TR-65-57

APPENDIX B

Calculated Stresses in Free-Standing Cylindrical Shells of Pyrolytic Graphite

NOTE: See Appendix F for definitions of symbols used in this Appendix.

AFRPL-TR-65-57

APPENDIX B

PHYSICAL PROPERTIES INPUT DATA

Pyrolytic Graphite:*	Young's Modulus	$E_a = 4.5 \times 10^6$ psi
	Young's Modulus	$E_c = 1.5 \times 10^6$ psi
	Poisson's Ratio	$\nu_{ac} = 0.90$
	Poisson's Ratio	$\nu_{ca} = 0.30$
	Poisson's Ratio	$\nu_{aa} = -0.16$
	Shear Modulus	$G_a = 0.2 \times 10^6$ psi
	Shear Modulus	$G_c = 2.68 \times 10^6$ psi
	Total Thermal Expansion $\alpha_a \Delta T$	$= -0.00144$ in/in
	Total Thermal Expansion $\alpha_c \Delta T$	$= -0.0432$ in/in

* Reference 7.

CASE NO. 1

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .56000000, 00 RO .59000000, 00 PI .00000000, 00 PO .00000000, 00
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -.14502890,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.56000000, 00	.50000000,-01	.51168800, 04	-.85496000, 03
.56150000, 00	.13010000, 02	.45881900, 04	-.76870000, 03
.56300000, 00	.24490000, 02	.40623600, 04	-.67424000, 03
.56450000, 00	.34530000, 02	.35394200, 04	-.58153000, 03
.56600000, 00	.43130000, 02	.30193000, 04	-.49057000, 03
.56750000, 00	.50320000, 02	.25019800, 04	-.40124000, 03
.56900000, 00	.56090000, 02	.19874100, 04	-.31381000, 03
.57050000, 00	.60510000, 02	.14756100, 04	-.22794000, 03
.57200000, 00	.63530000, 02	.96646000, 03	-.143 6000, 03
.57350000, 00	.65240000, 02	.46004000, 03	-.61190000, 02
.57500000, 00	.65620000, 02	-.43750000, 02	.19750000, 02
.57650000, 00	.64680000, 02	-.54492000, 03	.99090000, 02
.57800000, 00	.62450000, 02	-.10434800, 04	.17687000, 03
.57950000, 00	.58940000, 02	-.15395100, 04	.25307000, 03
.58100000, 00	.54180000, 02	-.20329800, 04	.32774000, 03
.58250000, 00	.48150000, 02	-.25239900, 04	.40087000, 03
.58400000, 00	.40940000, 02	-.30124200, 04	.47253000, 03
.58550000, 00	.32500000, 02	-.34984400, 04	.54270000, 03
.58700000, 00	.22840000, 02	-.39820600, 04	.61139000, 03
.58850000, 00	.12020000, 02	-.44632600, 04	.67864000, 03
.59000000, 00	.40000000,-01	-.49420500, 04	.74446000, 03

CASE NO. 2

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .26000000, 00 RO .61000000, 00 PI .00000000, 00 PO .00000000, 00
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06
 AXIAL STRAIN -.14676110,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.56000000, 00	.40000000,-01	.84692500, 04	-.14792800, 04
.56250000, 00	.35690000, 02	.75752400, 04	-.13041600, 04
.56500000, 00	.67100000, 02	.66894900, 04	-.11341800, 04
.56750000, 00	.94330000, 02	.58118300, 04	-.96924000, 03
.57000000, 00	.11751000, 03	.49421300, 04	-.80923000, 03
.57250000, 00	.13668000, 03	.40802000, 04	-.65407000, 03
.57500000, 00	.15197000, 03	.32259500, 04	-.50363000, 03
.57750000, 00	.16344000, 03	.23792400, 04	-.35782000, 03
.58000000, 00	.17118000, 03	.15398900, 04	-.21657000, 03
.58250000, 00	.17526000, 03	.70781000, 03	-.79770000, 02
.58500000, 00	.17578000, 03	-.11709000, 03	.52690000, 02
.58750000, 00	.17280000, 03	-.93501000, 03	.18087000, 03
.59000000, 00	.16637000, 03	-.17460700, 04	.30486000, 03
.59250000, 00	.15661000, 03	-.25503200, 04	.42475000, 03
.59500000, 00	.14354000, 03	-.33479700, 04	.54062000, 03
.59750000, 00	.12729000, 03	-.41390200, 04	.65256000, 03
.60000000, 00	.10788000, 03	-.49236900, 04	.76063000, 03
.60250000, 00	.85380000, 02	-.57020300, 04	.86492000, 03
.60500000, 00	.59870000, 02	-.64741600, 04	.96550000, 03
.60750000, 00	.31410000, 02	-.72401800, 04	.10624500, 04
.61000000, 00	.50000000,-01	-.80002100, 04	.11558300, 04

CASE NO. 3

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 A1-.14400000,-02 AA2-.43200000,-01
 R1 .56000000, 00 R0 .64000000, 00 P1 .00000000, 00 P0 .00000000, 00
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.15070110,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.56000000, 00	.30000000,-01	.13400550, 05	-.24456000, 04
.56400000, 00	.89890000, 02	.11940800, 05	-.21311700, 04
.56800000, 00	.16826000, 03	.10502910, 05	-.18305700, 04
.57200000, 00	.23557000, 03	.90062900, 04	-.15433300, 04
.57600000, 00	.29217000, 03	.76903200, 04	-.12690400, 04
.58000000, 00	.33844000, 03	.63143900, 04	-.10072500, 04
.58400000, 00	.37473000, 03	.49579700, 04	-.75757000, 03
.58800000, 00	.40134000, 03	.36204400, 04	-.51962000, 03
.59200000, 00	.41862000, 03	.23013700, 04	-.29300000, 03
.59600000, 00	.42689000, 03	.10001800, 04	-.77380000, 02
.60000000, 00	.42642000, 03	-.28363000, 03	.12761000, 03
.60400000, 00	.41750000, 03	-.15505100, 04	.32228000, 03
.60800000, 00	.40044000, 03	-.28008600, 04	.50699000, 03
.61200000, 00	.37548000, 03	-.40352000, 04	.68202000, 03
.61600000, 00	.34288000, 03	-.52539400, 04	.84767000, 03
.62000000, 00	.30287000, 03	-.64574800, 04	.10042300, 04
.62400000, 00	.25572000, 03	-.76462100, 04	.11520000, 04
.62800000, 00	.20163000, 03	-.88205300, 04	.12912100, 04
.63200000, 00	.14086000, 03	-.99808100, 04	.14221500, 04
.63600000, 00	.73600000, 02	-.11127370, 05	.15450700, 04
.64000000, 00	.40000000,-01	-.12260610, 05	.16601800, 04

CASE NO. 4

E1 .45000000. 07 E2 .15000000. 07 NU1 .30000000. 00 NU2 .90000000. 00 NU3-.16000000. 00

G1 .26785714. 07 G2 .20000000. 06 AA1-.14400000.-02 AA2-.43200000.-01

R1 .11500000. 01 R0 .11800000. 01 P1 .00000000. 00 PO .00000000. 00

C11 .63076036. 07 C12 .21774193. 07 C13 .95046082. 06 C22 .28064516. 07 C44 .20000000. 06

B1-.10451612. 06 B2-.12750966. 06

AXIAL STRAIN --.14425476.-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.11500000. 01	.20000000.-01	.25039100. 04	-.41207000. 03
.11515000. 01	.31200000. 01	.22494600. 04	-.36856000. 03
.11530000. 01	.58700000. 01	.19956400. 04	-.32548000. 03
.11545000. 01	.83000000. 01	.17425300. 04	-.28280000. 03
.11560000. 01	.10380000. 02	.14900600. 04	-.24053000. 03
.11575000. 01	.12140000. 02	.12382500. 04	-.19866000. 03
.11590000. 01	.13550700. 02	.98710000. 03	-.15719000. 03
.11605000. 01	.14660000. 02	.73661000. 03	-.11612000. 03
.11620000. 01	.15430000. 02	.48676000. 03	-.75450000. 02
.11635000. 01	.15870000. 02	.23756000. 03	-.35180000. 02
.11650000. 01	.16000000. 02	-.10990000. 02	.47000000. 01
.11665000. 01	.15800000. 02	-.25891000. 03	.44190000. 02
.11680000. 01	.15300000. 02	-.50619000. 03	.83300000. 02
.11695000. 01	.14480000. 02	-.75284000. 03	.12202000. 03
.11710000. 01	.13330000. 02	-.99887000. 03	.16035000. 03
.11725000. 01	.11880000. 02	-.12442600. 04	.19831000. 03
.11740000. 01	.10120000. 02	-.14890300. 04	.23589000. 03
.11755000. 01	.80500000. 01	-.17331900. 04	.27309000. 03
.11770000. 01	.56700000. 01	-.19767300. 04	.30992000. 03
.11785000. 01	.30000000. 01	-.22196500. 04	.34638000. 03
.11800000. 01	.20000000.-01	-.24619700. 04	.38247000. 03

CASE NO. 5

E1 .45000000. 07 E2 .15000000. 07 NU1 .30000000. 00 NU2 .90000000. 00 NU3-.16000000. 00

G1 .26785714. 07 G2 .20000000. 06 AA1-.14400000.-02 AA2-.43200000.-01

R1 .11500000. 01 R0 .12000000. 01 P1 .00000000. 00 P0 .00000000. 00

C11 .63076036. 07 C12 .21774193. 07 C13 .95046082. 06 C22 .28064516. 07 C44 .20000000. 06

B1-.10451612. 06 B2-.12750966. 06

AXIAL STRAIN --.14468738.-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.11500000. 01	.10000000.-01	.41604400. 04	-.69659000. 03
.11525000. 01	.85800000. 01	.37331800. 04	-.62051000. 03
.11550000. 01	.16180000. 02	.33077900. 04	-.54561000. 03
.11575000. 01	.22830000. 02	.28842700. 04	-.47186000. 03
.11600000. 01	.28550000. 02	.24626200. 04	-.39926000. 03
.11625000. 01	.33330000. 02	.20428000. 04	-.32778000. 03
.11650000. 01	.37200000. 02	.16248100. 04	-.25742000. 03
.11675000. 01	.40150000. 02	.12086200. 04	-.18817000. 03
.11700000. 01	.42190000. 02	.79420000. 03	-.12003000. 03
.11725000. 01	.43360000. 02	.38159000. 03	-.52950000. 02
.11750000. 01	.43640000. 02	-.29280000. 02	.13040000. 02
.11775000. 01	.43050000. 02	-.43840000. 03	.77970000. 02
.11800000. 01	.41600000. 02	-.84580000. 03	.14184000. 03
.11825000. 01	.39300000. 02	-.12514700. 04	.20468000. 03
.11850000. 01	.36150000. 02	-.16554600. 04	.26648000. 03
.11875000. 01	.32170000. 02	-.20577500. 04	.32726000. 03
.11900000. 01	.27350000. 02	-.24583800. 04	.38703000. 03
.11925000. 01	.21720000. 02	-.28573500. 04	.44580000. 03
.11950000. 01	.15280000. 02	-.32546900. 04	.50358000. 03
.11975000. 01	.80400000. 01	-.36503800. 04	.56038000. 03
.12000000. 01	.10000000.-01	-.40444700. 04	.61620000. 03

CASE NO. 6

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 A11-.14400000,-02 A2-.43200000,-01
 R1 .11500000, 01 R2 .12300000, 01 P1 .00000000, 00 P2 .00000000, 00
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.14571060,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.11500000, 01	.30000000,-01	.66241900, 04	-.11368200, 04
.11540000, 01	.21790000, 02	.59331300, 04	-.10066600, 04
.11580000, 01	.41020000, 02	.52469900, 04	-.87957000, 03
.11620000, 01	.57770000, 02	.45657300, 04	-.75550000, 03
.11660000, 01	.72070000, 02	.38892400, 04	-.63439000, 03
.11700000, 01	.83970000, 02	.32174900, 04	-.51620000, 03
.11740000, 01	.93510000, 02	.25504000, 04	-.40088000, 03
.11780000, 01	.10073000, 03	.18879100, 04	-.28838000, 03
.11820000, 01	.10566000, 03	.12299500, 04	-.17867000, 03
.11860000, 01	.10835000, 03	.57645000, 03	-.71690000, 02
.11900000, 01	.10883000, 03	-.72650000, 02	.32600000, 02
.11940000, 01	.10714000, 03	-.71739000, 03	.13424000, 03
.11980000, 01	.10331000, 03	-.13578700, 04	.23327000, 03
.12020000, 01	.97380000, 02	-.19941100, 04	.32973000, 03
.12060000, 01	.89410000, 02	-.26261700, 04	.42368000, 03
.12100000, 01	.79390000, 02	-.32541400, 04	.51514000, 03
.12140000, 01	.67370000, 02	-.38780400, 04	.60415000, 03
.12180000, 01	.53400000, 02	-.44979300, 04	.69076000, 03
.12220000, 01	.37490000, 02	-.51138800, 04	.77499000, 03
.12260000, 01	.19680000, 02	-.57259500, 04	.85689000, 03
.12300000, 01	.20000000,-01	-.63341500, 04	.93650000, 03

CASE NO. 7

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .10000000, 00 R0 .10000000, 01 P1 .00000000, 00 P0 .00000000, 00

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.69805780,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.10000000, 00	.20000000,-01	.20608602, 06	-.57906330, 05
.14500000, 00	.46395820, 05	.11086734, 06	-.91513000, 03
.19000000, 00	.56721000, 05	.73490920, 05	.14357760, 05
.23500000, 00	.5772280, 05	.52494670, 05	.18663310, 05
.28000000, 00	.55699900, 05	.37970370, 05	.19122060, 05
.32500000, 00	.52432100, 05	.26608910, 05	.17998870, 05
.37000000, 00	.48695670, 05	.17043560, 05	.16166540, 05
.41500000, 00	.44798340, 05	.86184000, 04	.14006970, 05
.46000000, 00	.40879990, 05	.98074000, 03	.11702480, 05
.50500000, 00	.37006430, 05	-.60767400, 04	.93454700, 04
.55000000, 00	.33208390, 05	-.12685020, 05	.69845600, 04
.59500000, 00	.29499160, 05	-.18931920, 05	.46457600, 04
.64000000, 00	.25883170, 05	-.24879140, 05	.23429300, 04
.68500000, 00	.22360130, 05	-.30572020, 05	.83050000, 02
.73000000, 00	.18927450, 05	-.36044820, 05	-.21307100, 04
.77500000, 00	.15581350, 05	-.41324370, 05	-.42974800, 04
.82000000, 00	.12317590, 05	-.46432020, 05	-.64166400, 04
.86500000, 00	.91317700, 04	-.51385270, 05	-.84923600, 04
.91000000, 00	.60196100, 04	-.56198580, 05	-.10523180, 05
.95500000, 00	.29770100, 04	-.60884120, 05	-.12511830, 05
.10000000, 01	.20000000,-01	-.65452390, 05	-.14460190, 05

CASE NO. 8

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .11200000, 01 RO .12200000, 01 PI .00000000, 00 PO .00000000, 00
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN

--.14676027,-02

R	SIGMA R	SIGMA THETA	SIGMA Z
.11200000, 01	.20000000,-01	.84693100, 04	-.14792700, 04
.11250000, 01	.35670900, 02	.75753000, 04	-.13041500, 04
.11300000, 01	.67080000, 02	.66895500, 04	-.11341600, 04
.11350000, 01	.94320000, 02	.58116700, 04	-.96923000, 03
.11400000, 01	.11749000, 03	.49421600, 04	-.80922000, 03
.11450000, 01	.13667000, 03	.40802500, 04	-.65405000, 03
.11500000, 01	.15196000, 03	.32260000, 04	-.50361000, 03
.11550000, 01	.16344000, 03	.23793000, 04	-.35781000, 03
.11600000, 01	.17116000, 03	.15399600, 04	-.21656000, 03
.11650000, 01	.17525000, 03	.70789000, 03	-.79750000, 02
.11700000, 01	.17576000, 03	-.11705000, 03	.52700000, 02
.11750000, 01	.17277000, 03	-.93497000, 03	.18088000, 03
.11800000, 01	.16636000, 03	-.17460100, 04	.30488000, 03
.11850000, 01	.15659000, 03	-.25502700, 04	.42477000, 03
.11900000, 01	.14354000, 03	-.33479000, 04	.54064000, 03
.11950000, 01	.12728000, 03	-.41389900, 04	.65258000, 03
.12000000, 01	.10787000, 03	-.49236400, 04	.76065000, 03
.12050000, 01	.85370000, 02	-.57019900, 04	.86494000, 03
.12100000, 01	.59860000, 02	-.64741400, 04	.96552000, 03
.12150000, 01	.31380000, 02	-.72401600, 04	.10624600, 04
.12200000, 01	.30000000,-01	-.80001700, 04	.11558400, 04

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILLED.

AFRPL-TR-65-57

APPENDIX C

Calculated Stresses in Composite Cylinders with Pyrolytic Graphite Coating on the Inside

NOTE: See Appendix F for definitions of symbols used in this Appendix.

AFRPL-TR-65-57

APPENDIX C

PHYSICAL PROPERTIES INPUT DATA

Pyrolytic Graphite:*	Young's Modulus	$E_a = 4.5 \times 10^6$ psi
	Young's Modulus	$E_c = 1.5 \times 10^6$ psi
	Poisson's Ratio	$\nu_{ac} = 0.90$
	Poisson's Ratio	$\nu_{ca} = 0.30$
	Poisson's Ratio	$\nu_{aa} = -0.16$
	Shear Modulus	$G_a = 0.2 \times 10^6$ psi
	Shear Modulus	$G_c = 2.68 \times 10^6$ psi
	Total Thermal Expansion	$\alpha_a \Delta T = -0.00144$ in/in
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0432$ in/in
Molded Graphite:**	Young's Modulus	$E = 1.5 \times 10^6$ psi
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.0046$ in/in
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0070$ in/in
Extruded Graphite:**	Young's Modulus	$E = 1.5 \times 10^6$ psi
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.0044$ in/in
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0076$ in/in

* Reference 7.

** Reference 9.

CASE NO. 1

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1-.26785714, 07 G2-.20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .56000000, 00 R0 .59000000, 00 E .15000000, 07 NU .35000000, 00

GR-.46000000,-02 GTHETA-.46000000,-02 GZ-.70000000,-02 RG .99000000, 00

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000,

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.63115496,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.30000000,-01	-.16496400, 04	-.21658000, 05	-.14429274,-02
.56150000, 00	-.49700000, 01	-.20967400, 04	-.21590970, 05	-.15006805,-02
.56300000, 00	-.11140000, 02	-.25415000, 04	-.21525360, 05	-.15583257,-02
.56450000, 00	-.18440000, 02	-.29839200, 04	-.21461140, 05	-.16158634,-02
.56600000, 00	-.26880000, 02	-.34240500, 04	-.21398320, 05	-.16732950,-02
.56750000, 00	-.36440000, 02	-.38619200, 04	-.21336870, 05	-.17306246,-02
.56900000, 00	-.47110000, 02	-.42975400, 04	-.21276770, 05	-.17878513,-02
.57050000, 00	-.58850000, 02	-.47309100, 04	-.21218000, 05	-.18449739,-02
.57200000, 00	-.71680000, 02	-.51621200, 04	-.21160550, 05	-.19020005,-02
.57350000, 00	-.85550000, 02	-.55911100, 04	-.21104390, 05	-.19589252,-02
.57500000, 00	-.10046000, 03	-.60179500, 04	-.21049520, 05	-.20157528,-02
.57650000, 00	-.11641000, 03	-.64426700, 04	-.20995920, 05	-.20724854,-02
.57800000, 00	-.13338000, 03	-.68652900, 04	-.20943570, 05	-.21291231,-02
.57950000, 00	-.15136000, 03	-.72858300, 04	-.20892460, 05	-.21856677,-02
.58100000, 00	-.17030000, 03	-.77042700, 04	-.20842570, 05	-.22421163,-02
.58250000, 00	-.19026000, 03	-.81207200, 04	-.20793890, 05	-.22984820,-02
.58400000, 00	-.21115000, 03	-.85351100, 04	-.20746390, 05	-.23547516,-02
.58550000, 00	-.23300000, 03	-.89475000, 04	-.20700080, 05	-.24109342,-02
.58700000, 00	-.25580000, 03	-.93579300, 04	-.20654930, 05	-.24670299,-02
.58850000, 00	-.27953000, 03	-.97664000, 04	-.20610930, 05	-.25230395,-02
.59000000, 00	-.30415000, 03	-.10172910, 05	-.20568050, 05	-.25789631,-02
.59000000, 00	-.30420774, 03	.63932355, 03	.11499661, 04	-.25789655,-02
.67000000, 00	-.19827329, 03	.5338914, 03	.11499661, 04	-.29925341,-02
.75000000, 00	-.12439162, 03	.45950748, 03	.11499661, 04	-.33997218,-02
.83000000, 00	-.70824666, 02	.40594011, 03	.11499660, 04	-.38023735,-02
.91000000, 00	-.30753407, 02	.36586925, 03	.11499661, 04	-.42016854,-02
.99000000, 00	-.19259259,-02	.33511392, 03	.11499661, 04	-.45984675,-02

CASE NO. 2

E1 .45000000. 07 E2 .15000000. 07 MU1 .30000000. 00 MU2 .90000000. 00 MU3 .16000000. 00

G1 .26785714. 07 G2 .20000000. 06 AA1 .14400000. 03 AA2 .43200000. 01

RT .56000000. 00 RD .61000000. 00 E .15000000. 07 NU .35000000. 00

GR .46000000. 02 GTHETA .44000000. 02 GZ .70000000. 02 RG .10100000. 01

C11 .63076036. 07 C12 .21774193. 07 C13 .95046082. 06 C22 .28064516. 07 C44 .20000000. 06

01 .10451612. 06 B2 .12750966. 06

AXIAL STRAIN --.59118982. 02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000. 00	.20000000. 01	.33691400. 04	-.20662580. 05	-.79854790. 03
.56250000. 00	.13270000. 02	.25943800. 04	-.20526690. 05	-.89773040. 03
.56500000. 00	.22990000. 02	.18265900. 04	-.20395100. 05	-.99657510. 03
.56750000. 00	.29250000. 02	.10656500. 04	-.20267710. 05	-.10950881. 02
.57000000. 00	.32150000. 02	.31145000. 05	-.20144430. 05	-.11932760. 02
.57250000. 00	.31740000. 02	-.43618000. 03	-.20025190. 05	-.12911499. 02
.57500000. 00	.28090000. 02	-.11773100. 04	-.19909890. 05	-.13887128. 02
.57750000. 00	.21280000. 02	-.19120800. 04	-.19798460. 05	-.14859707. 02
.58000000. 00	.11360000. 02	-.26406100. 04	-.19690810. 05	-.15829337. 02
.58250000. 00	-.15800000. 01	-.33629900. 04	-.19586870. 05	-.16796046. 02
.58500000. 00	-.17460000. 02	-.60795100. 04	-.19486560. 05	-.17759895. 02
.58750000. 00	-.36250000. 02	-.47897200. 04	-.19389810. 05	-.18720984. 02
.59000000. 00	-.57900000. 02	-.54943200. 04	-.19296560. 05	-.19679343. 02
.59250000. 00	-.82300000. 02	-.61931500. 04	-.19206710. 05	-.20635013. 02
.59500000. 00	-.10946000. 03	-.68864000. 04	-.19120220. 05	-.21588112. 02
.59750000. 00	-.13923000. 03	-.75740700. 04	-.19037000. 05	-.22538611. 02
.60000000. 00	-.17165000. 03	-.82565300. 04	-.18957000. 05	-.23486650. 02
.60250000. 00	-.20659000. 03	-.89332300. 04	-.18880150. 05	-.24432220. 02
.60500000. 00	-.24405000. 03	-.96048800. 04	-.18806400. 05	-.25375409. 02
.60750000. 00	-.28395000. 03	-.10271360. 05	-.18735670. 05	-.26316258. 02
.61000000. 00	-.32622000. 03	-.10932750. 05	-.18667900. 05	-.27254827. 02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.61000000. 00	-.32625570. 03	.70095259. 03	.17632966. 04	-.27254848. 02
.69000000. 00	-.21406303. 03	.58876029. 03	.17632967. 04	-.31525969. 02
.77000000. 00	-.13498581. 03	.50968307. 03	.17632967. 04	-.35729159. 02
.85000000. 00	-.77166370. 02	.45186362. 03	.17632967. 04	-.39883598. 02
.93000000. 00	-.33615925. 02	.40831281. 03	.17632966. 04	-.44001867. 02
.10100000. 01	-.21851851. 02	.37469587. 03	.17632967. 04	-.48892561. 02

CASE NO. 3

F1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1 .14400000, 02 AA2 .43200000, 01

R1 .56000000, 00 R0 .64000000, 00 E .15000000, 07 NU .35000000, 00

GR .46000000, 02 GTHEIA .46000000, 02 GZ .70000000, 02 RG .19400000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1 .10451612, 06 B2 .12750966, 06

AXIAL STRAIN -.54064728, 02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000, 01	.10168390, 05	-.19476040, 05	.71206300, 04
.56400000, 00	.67510000, 02	.88667500, 04	-.19207040, 05	-.93642100, 04
.55800000, 00	.12496000, 03	.75844200, 04	-.18950180, 05	-.25750150, 03
.57200000, 00	.17268000, 03	.63208600, 04	-.18705050, 05	-.42040350, 03
.57600000, 00	.21106000, 03	.50755000, 04	-.18471260, 05	.58237550, 03
.58000000, 00	.24035000, 03	.38479000, 04	-.18248470, 05	-.74345350, 03
.58400000, 00	.26093000, 03	.26375000, 04	-.18036290, 05	-.90366040, 03
.58800000, 00	.27302000, 03	.14437800, 04	-.17834420, 05	-.10630314, 02
.59200000, 00	.27694000, 03	.26630000, 03	-.17642500, 05	-.12215904, 02
.59600000, 00	.27297000, 03	-.89533000, 03	-.17460210, 05	-.13793604, 02
.60000000, 00	.26135000, 03	-.20416300, 04	-.17287250, 05	.15363793, 02
.60400000, 00	.24233000, 03	-.31729800, 04	-.17123360, 05	-.16926513, 02
.60800000, 00	.21619000, 03	-.42897400, 04	-.16968200, 05	-.18482143, 02
.61200000, 00	.18313000, 03	-.53923600, 04	-.16821540, 05	-.20030913, 02
.61600000, 00	.14338000, 03	-.64811600, 04	-.16643100, 05	-.21573032, 02
.62000000, 00	.97160000, 02	-.75565900, 04	-.16552630, 05	-.23108712, 02
.62400000, 00	.44690000, 02	-.86189100, 04	-.16429880, 05	.24638172, 02
.62800000, 00	-.13840000, 02	-.96684900, 04	-.16314630, 05	-.26161612, 02
.63200000, 00	-.78250000, 02	-.10705700, 05	-.16206640, 05	-.27679261, 02
.63600000, 00	-.14831000, 03	-.11730750, 05	-.16105680, 05	-.29191251, 02
.64000000, 00	-.22387000, 03	-.12744050, 05	-.16011560, 05	-.30697831, 02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.64000000, 00	-.22390599, 03	.49686466, 03	.24858262, 04	-.30697845, 02
.72000000, 00	-.14826981, 03	.42122811, 03	.24858259, 04	-.35025200, 02
.80000000, 00	-.94167444, 02	.36712574, 03	.24858259, 04	-.39306425, 02
.88000000, 00	-.54137888, 02	.32709618, 03	.24858259, 04	-.43554102, 02
.96000000, 00	-.23692111, 02	.29665040, 03	.24858259, 04	-.47776617, 02
.10400000, 01	-.18888888, 02	.27295640, 03	.24858259, 04	-.51979778, 02

CASE NO. 4

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1 .14400000, 02 AA2 .43200000, 01

R1 .56000000, 00 R0 .59000000, 00 E .15000000, 07 NU .35000000, 00

GR .46000000, 02 GTHETA .46000000, 02 G2 .70000000, 02 RG .12900000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

E1 .10451612, 06 B2 .12750966, 06

AXIAL STRAIN -.66415364, 02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.30000000, 01	-.14697200, 04	-.23171730, 05	-.14506772, 02
.56150000, 00	-.44800000, 01	-.19129900, 04	-.23104870, 05	-.15080305, 02
.56300000, 00	-.10160000, 02	-.23539300, 04	-.23039430, 05	-.15652768, 02
.56450000, 00	-.16960000, 02	-.27925500, 04	-.22975380, 05	-.16224152, 02
.56600000, 00	-.24890000, 02	-.32288900, 04	-.22912700, 05	-.16794494, 02
.56750000, 00	-.33940000, 02	-.36630000, 04	-.22851390, 05	-.17363815, 02
.56900000, 00	-.44080000, 02	-.40948400, 04	-.22791410, 05	-.17932096, 02
.57050000, 00	-.55290000, 02	-.45244900, 04	-.22732760, 05	-.18499377, 02
.57200000, 00	-.67590000, 02	-.49519900, 04	-.22675420, 05	-.19065688, 02
.57350000, 00	-.80910000, 02	-.53772800, 04	-.22619370, 05	-.19630979, 02
.57500000, 00	-.95280000, 02	-.58004400, 04	-.22564600, 05	-.20195310, 02
.57650000, 00	-.11067000, 03	-.62214900, 04	-.22511080, 05	-.20758691, 02
.57800000, 00	-.12707000, 03	-.66404400, 04	-.22458800, 05	-.21321122, 02
.57950000, 00	-.14447000, 03	-.70573400, 04	-.22407760, 05	-.21882643, 02
.58100000, 00	-.16284000, 03	-.74721700, 04	-.22357930, 05	-.22443224, 02
.58250000, 00	-.18222000, 03	-.78850100, 04	-.22309310, 05	-.23002934, 02
.58400000, 00	-.20252000, 03	-.82957900, 04	-.22261850, 05	-.23561785, 02
.58550000, 00	-.22377000, 03	-.87046100, 04	-.22215580, 05	-.24119616, 02
.58700000, 00	-.24598000, 03	-.91114900, 04	-.22170460, 05	-.24676677, 02
.58850000, 00	-.26909000, 03	-.95164200, 04	-.22126470, 05	-.25232878, 02
.59000000, 00	-.29312000, 03	-.99194000, 04	-.22083620, 05	-.25788209, 02
.59000000, 00	-.29316081, 03	-.44825607, 03	.59197874, 03	-.25788231, 02
.73000000, 00	-.16460592, 03	.31970118, 03	.59197874, 03	-.32752080, 02
.87000000, 00	-.92942036, 02	.24803729, 03	.59197874, 03	-.39594428, 02
.10100000, 01	-.48953481, 02	.20404838, 03	.59197862, 03	-.46365803, 02
.11500000, 01	-.20027925, 02	.17512318, 03	.59197874, 03	-.53092124, 02
.12900000, 01	-.18518518, 02	.15509305, 03	.59197862, 03	-.59188860, 02

CASE NO. 5

E1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1 .14400000, 02 AA2 .43200000, 01

R1 .56000000, 00 R0 .61000000, 00 E .15000000, 07 NU .35000000, 00

GR .46000000, 02 GTHETA .46000000, 02 GZ .70000000, 02 RG .13100000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1 .10451612, 06 B2 .12750966, 06

AXIAL STRAIN -.64053400, 02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.30000000, 01	.36736100, 04	-.22931780, 05	-.80584070, 03
.56250000, 00	.14650000, 02	.29082400, 04	-.22796160, 05	-.90404210, 03
.56500000, 00	.25760000, 02	.21497700, 04	-.22664800, 05	-.10019076, 02
.56750000, 00	.33460000, 02	.13980900, 04	-.22537600, 05	-.10994435, 02
.57000000, 00	.37820000, 02	.65307000, 03	-.22414470, 05	-.11966571, 02
.57250000, 00	.38900000, 02	-.85440000, 02	-.22295350, 05	-.12935584, 02
.57500000, 00	.36760000, 02	-.81753000, 03	-.22180140, 05	-.13901506, 02
.57750000, 00	.31490000, 02	-.15433000, 04	-.22068760, 05	-.14864398, 02
.58000000, 00	.23140000, 02	-.22629100, 04	-.21961130, 05	-.15824371, 02
.58250000, 00	.11790000, 02	-.29764200, 04	-.21857180, 05	-.16781423, 02
.58500000, 00	-.24800000, 01	-.36899300, 04	-.21756830, 05	-.17735645, 02
.58750000, 00	-.19650000, 02	-.43856000, 04	-.21660010, 05	-.18687107, 02
.59000000, 00	-.39620000, 02	-.50815000, 04	-.21566650, 05	-.19635870, 02
.59250000, 00	-.62350000, 02	-.57717100, 04	-.21476670, 05	-.20581962, 02
.59500000, 00	-.87790000, 02	-.64563700, 04	-.21390010, 05	-.21525484, 02
.59750000, 00	-.11585000, 03	-.71355300, 04	-.21306610, 05	-.22466437, 02
.60000000, 00	-.14650000, 03	-.78993200, 04	-.21226390, 05	-.23404929, 02
.60250000, 00	-.17968000, 03	-.84778100, 04	-.21149290, 05	-.24340981, 02
.60500000, 00	-.21535000, 03	-.91411000, 04	-.21075260, 05	-.25274663, 02
.60750000, 00	-.25344000, 03	-.97992600, 04	-.21004230, 05	-.26206006, 02
.61000000, 00	-.29391000, 03	-.10452420, 05	-.20936150, 05	-.27135098, 02
R				
	SIGMA R	SIGMA THETA	SIGMA Z	U R
.61000000, 00	-.29392903, 03	.45668829, 03	.94895573, 03	-.27135122, 02
.75000000, 00	-.16689103, 03	.32965064, 03	.94895588, 03	-.34220360, 02
.89000000, 00	-.94926666, 02	.25768631, 03	.94895588, 03	-.41184596, 02
.10300000, 01	-.50255925, 02	.21301555, 03	.94895588, 03	-.48077169, 02
.11700000, 01	-.20638148, 02	.18339777, 03	.94895588, 03	-.54923806, 02
.13100000, 01	-.20740740, 02	.16275755, 03	.94895588, 03	-.61739233, 02

CASE NO. 6

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3 .1600000, 00

G1 .26785714, 07 G2 .2000000, 06 AA1 .1440000, 02 AA2 .4320000, 01

R1 .5600000, 00 R2 .6400000, 00 E .1500000, 07 NU .3500000, 00

GR .4600000, 02 GTHEIA .4600000, 02 GZ .7000000, 02 RG .1340000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .2000000, 06

B1 .10451612, 06 B2 .12750966, 06

AXIAL STRAIN -.60746317, -02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.5600000, 00	.0000000, 00	.10607490, 05	-.22553020, 05	.64585800, -04
.5640000, 00	.7069000, 02	.93259600, 04	-.22284370, 05	-.98156000, -04
.5680000, 00	.1314000, 03	.80635100, 04	-.22027740, 05	-.25991580, -03
.5720000, 00	.1825100, 03	.68196100, 04	-.21782710, 05	-.42072440, -03
.5760000, 00	.2243500, 03	.55937200, 04	-.21548920, 05	-.58061040, -03
.5800000, 00	.2572000, 03	.43853000, 04	-.21326010, 05	-.73960890, -03
.5840000, 00	.2813900, 03	.31939000, 04	-.21113610, 05	-.89774250, -03
.5880000, 00	.2971900, 03	.20189800, 04	-.20911400, 05	-.10550451, -02
.5920000, 00	.3049000, 03	.86012000, 03	-.20719050, 05	-.111597, -02
.5960000, 00	.3047800, 03	-.28311000, 03	-.20536240, 05	-.1367773, -02
.6000000, 00	.2970900, 03	-.14111700, 04	-.20362670, 05	-.15222119, -02
.6040000, 00	.2820800, 03	-.25244500, 04	-.20198050, 05	-.16764395, -02
.6080000, 00	.2606100, 03	-.36233400, 04	-.20042090, 05	-.18299581, -02
.6120000, 00	.2310700, 03	-.47082600, 04	-.19894550, 05	-.19827937, -02
.6160000, 00	.1955100, 03	-.57795700, 04	-.19755150, 05	-.21349693, -02
.6200000, 00	.1535400, 03	-.68376000, 04	-.19623630, 05	-.22865029, -02
.6240000, 00	.1053800, 03	-.78827200, 04	-.19499760, 05	-.24374189, -02
.6280000, 00	.5120000, 02	-.89152700, 04	-.19383320, 05	-.25877351, -02
.6320000, 00	-.8790000, 01	-.99355700, 04	-.19274060, 05	-.27374756, -02
.6360000, 00	-.7439000, 02	-.10943890, 05	-.19171770, 05	-.28866532, -02
.6400000, 00	-.1454600, 03	-.11940590, 05	-.19076250, 05	-.30352918, -02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.6400000, 00	-.14547814, 03	.23146818, 03	.14181489, 04	-.30352924, -02
.7800000, 00	-.83892925, 02	.16988296, 03	.14181489, 04	-.37424955, -02
.9200000, 00	-.48213148, 02	.13420318, 03	.14181489, 04	-.44437683, -02
.1060000, 01	-.25711481, 02	.11170151, 03	.14181489, 04	-.51414606, -02
.1200000, 01	-.10615148, 02	.96605185, 02	.14181489, 04	-.58368254, -02
.1340000, 01	.15925925, 02	.85988036, 02	.14181489, 04	-.65305924, -02

~~G1-26785714, 07 G2-20000000, 06 AA1-14400000, 02 AA2-43200000, 01~~

5R-4600000,-02 GTHETA-4600000,-02 GZ-7000000,-02 RG-15800000,-01

81-10451612, 06 82-.12750966, 06

AXIAL STRAIN -0.62569561,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.3000000, -01	-.59841300, 04	-.20718820, 05	-.40324532, -02
.11515000, 01	-.79100000, 01	-.61968500, 04	-.20691920, 05	-.40892171, -02
.11530000, 01	-.16100000, 02	-.64090600, 04	-.20665340, 05	-.41459370, -02
.11545000, 01	-.24550000, 02	-.66207100, 04	-.20639080, 05	-.42026050, -02
.11560000, 01	-.33240000, 02	-.68318600, 04	-.20613120, 05	-.42592289, -02
.11575000, 01	-.42190000, 02	-.70424800, 04	-.20587480, 05	-.43158058, -02
.11590000, 01	-.51380000, 02	-.72525900, 04	-.20562130, 05	-.437323358, -02
.11605000, 01	-.60830000, 02	-.74621700, 04	-.20537100, 05	-.44288197, -02
.11620000, 01	-.70520000, 02	-.76712400, 04	-.20512360, 05	-.44852577, -02
.11635000, 01	-.80450000, 02	-.78798100, 04	-.20487940, 05	-.45416506, -02
.11650000, 01	-.90640000, 02	-.80878600, 04	-.20463810, 05	-.45979975, -02
.11665000, 01	-.10105000, 03	-.82954100, 04	-.20439980, 05	-.46543015, -02
.11680000, 01	-.11169000, 03	-.85024500, 04	-.20416440, 05	-.47105574, -02
.11695000, 01	-.12259000, 03	-.87909000, 04	-.20393200, 05	-.47667723, -02
.11710000, 01	-.13372000, 03	-.89150500, 04	-.20370250, 05	-.48229423, -02
.11725000, 01	-.14509000, 03	-.91206100, 04	-.20347590, 05	-.48790700, -02
.11740000, 01	-.15669000, 03	-.93256800, 04	-.20325220, 05	-.49351540, -02
.11755000, 01	-.16852000, 03	-.95302400, 04	-.20303130, 05	-.49911920, -02
.11770000, 01	-.18058000, 03	-.97343300, 04	-.20281330, 05	-.50471900, -02
.11785000, 01	-.19286000, 03	-.99379200, 04	-.20259810, 05	-.51031440, -02
.11800000, 01	-.20539000, 03	-.10141040, 05	-.20238580, 05	-.51590570, -02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11800000, 01	-.20541059, 03	.72355251, 03	.12959155, 04	-.51590577, -02
.12600000, 01	-.14830137, 03	.66644292, 03	.12959154, 04	-.55735864, -02
.13400000, 01	-.10111192, 03	.61925351, 03	.12959154, 04	-.59843754, -02
.14200000, 01	-.61671148, 02	.57981274, 03	.12959154, 04	-.63920568, -02
.15000000, 01	-.28371037, 02	.54651262, 03	.12959154, 04	-.67971279, -02
.15800000, 01	.77407437, 04	.51814151, 03	.12959154, 04	.71999850, -02

CASE NO. 8

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3-.1600000, 00

G1 .26785714, 07 G2 .2000000, 06 AA1-.1440000,-02 AA2-.4320000,-01

R1 .1150000, 01 RO .1200000, 01 E .1500000, 07 NU .3500000, 00

GR-.4600000,-02 GTHETA-.4600000,-02 GZ-.7000000,-02 RG .1600000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .2000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN ---.58507986,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.3000000,-01	-.32517500, 04	-.19328290, 05	-.32773228,-02
.11525000, 01	-.7420000, 01	-.36162200, 04	-.19276670, 05	-.33739601,-02
.11550000, 01	-.15630000, 02	-.39791500, 04	-.19225990, 05	-.34704545,-02
.11575000, 01	-.24580000, 02	-.43405600, 04	-.19176220, 05	-.35668084,-02
.11600000, 01	-.34270000, 02	-.47004500, 04	-.19127360, 05	-.36630213,-02
.11625000, 01	-.46907000, 02	-.50588400, 04	-.19079390, 05	-.37590947,-02
.11650000, 01	-.55830000, 02	-.54157500, 04	-.19032320, 05	-.38550321,-02
.11675000, 01	-.67690000, 02	-.57711800, 04	-.18966120, 05	-.39508325,-02
.11700000, 01	-.80260000, 02	-.61251700, 04	-.18940790, 05	-.40465029,-02
.11725000, 01	-.93520000, 02	-.64776900, 04	-.18896330, 05	-.41420353,-02
.11750000, 01	-.10748000, 03	-.68287800, 04	-.18852720, 05	-.42374386,-02
.11775000, 01	-.12212000, 03	-.71784500, 04	-.18809940, 05	-.43327130,-02
.11800000, 01	-.13740000, 03	-.75267100, 04	-.18768010, 05	-.44278584,-02
.11825000, 01	-.15343000, 03	-.78735700, 04	-.18726910, 05	-.45228768,-02
.11850000, 01	-.17007000, 03	-.82190400, 04	-.18686610, 05	-.46177692,-02
.11875000, 01	-.18738000, 03	-.85631300, 04	-.18647130, 05	-.47125360,-02
.11900000, 01	-.20534000, 03	-.89058700, 04	-.18608460, 05	-.48071840,-02
.11925000, 01	-.22393000, 03	-.92472600, 04	-.18570570, 05	-.49017090,-02
.11950000, 01	-.24318000, 03	-.95873100, 04	-.18533480, 05	-.49961140,-02
.11975000, 01	-.26304000, 03	-.99260300, 04	-.18497160, 05	-.50904000,-02
.12000000, 01	-.28352000, 03	-.10263430, 05	-.18461610, 05	-.51845670,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1200000, 01	-.28355122, 03	.10126941, 04	.19790021, 04	-.51845710,-02
.1280000, 01	-.20506781, 03	.93421029, 03	.19790019, 04	-.56206222,-02
.1360000, 01	-.14002233, 03	.86916522, 03	.19790021, 04	-.60515265,-02
.1440000, 01	-.85513888, 02	.81465640, 03	.19790019, 04	-.64781418,-02
.1520000, 01	-.39383111, 02	.76852596, 03	.19790021, 04	-.69811452,-02
.1600000, 01	.24444444,-02	.72914040, 03	.19790021, 04	-.73210786,-02

CASE NO. 9

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3-.1600000, 00

G1 .25785714, 07 G2 .2000000, 06 AA1-.1400000,-02 AA2-.4320000,-01

R1 .1150000, 01 R0 .1230000, 01 E .1500000, 07 NU .3500000, 00

GR-.4600000,-02 GTHETA-.4600000,-02 GZ-.7000000,-02 RG .1630000, 01

C11-.63076036, 07 C12-.21774193, 07 C13-.95046082, 06 C22-.28064516, 07 C44-.20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -.53440799,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.1000000,-01	.5568000, 03	-.17657430, 05	-.22357025,-02
.1154000, 01	.8900000, 00	-.4736000, 02	-.17559970, 05	-.23946170,-02
.1158000, 01	-.3100000, 00	-.6473300, 03	-.17465060, 05	-.25531265,-02
.1162000, 01	-.3570000, 01	-.12432100, 04	-.17372650, 05	-.27112400,-02
.1166000, 01	-.8830000, 01	-.18350300, 04	-.17282700, 05	-.28689635,-02
.1170000, 01	-.1608000, 02	-.24228600, 04	-.17195170, 05	-.30263031,-02
.1174000, 01	-.2528000, 02	-.30067400, 04	-.17110030, 05	-.31832626,-02
.1178000, 01	-.3639000, 02	-.35867300, 04	-.17027230, 05	-.33398521,-02
.1182000, 01	-.4937000, 02	-.41628800, 04	-.16946730, 05	-.34960756,-02
.1186000, 01	-.6421000, 02	-.47352600, 04	-.16868510, 05	-.36519411,-02
.1190000, 01	-.8088000, 02	-.53039100, 04	-.16792520, 05	-.38074537,-02
.1194000, 01	-.9932000, 02	-.5868800, 04	-.16718720, 05	-.39626202,-02
.1198000, 01	-.1195200, 03	-.64302300, 04	-.16647090, 05	-.41174467,-02
.1202000, 01	-.1414600, 03	-.69879900, 04	-.16577590, 05	-.42719372,-02
.1206000, 01	-.1650800, 03	-.75422300, 04	-.16510170, 05	-.44260990,-02
.1210000, 01	-.1903800, 03	-.80929800, 04	-.16444820, 05	-.45799360,-02
.1214000, 01	-.2173300, 03	-.86403000, 04	-.16381500, 05	-.473334550,-02
.1218000, 01	-.2458700, 03	-.91842100, 04	-.16320170, 05	-.48866610,-02
.1222000, 01	-.2760200, 03	-.97247900, 04	-.16260800, 05	-.50395600,-02
.1226000, 01	-.3077300, 03	-.10262080, 05	-.16203380, 05	-.51921590,-02
.1230000, 01	-.3409600, 03	-.10796090, 05	-.16147850, 05	-.53444580,-02
R				
.1230000, 01	-.34096296, 03	-.12428594, 04	-.27995370, 04	-.53444602,-02
.1310000, 01	-.24721303, 03	.11490855, 04	.27995370, 04	-.58024219,-02
.1390000, 01	-.16916296, 03	.10710394, 04	.27995370, 04	-.62546213,-02
.1470000, 01	-.10350548, 03	.10053820, 04	.27995370, 04	-.67014643,-02
.1550000, 01	-.47749629, 02	.94962614, 03	.27995370, 04	-.71439493,-02
.1630000, 01	.14814814,-03	.90187636, 03	.27995370, 04	-.75827181,-02

CASE NO. 10

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .11500000, 01 R0 .11800000, 01 E .15000000, 07 NU .35000000, 00

GR-.46000000,-07 GTHETA-.46000000,-02 GZ-.70000000,-02 RG .18800000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.65843025,-02-

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.11500000, 01	.20000000,-01	-.59420700, 04	-.22198610, 05	-.40822121,-02	
.11515000, 01	-.78500000, 01	-.61527600, 04	-.22171980, 05	-.41385451,-02	
.11530000, 01	-.15990000, 02	-.63629400, 04	-.22145680, 05	-.41948342,-02	
.11545000, 01	-.24370000, 02	-.65725700, 04	-.22119680, 05	-.42510722,-02	
.11560000, 01	-.33000000, 02	-.67817000, 04	-.22093990, 05	-.43072672,-02	
.11575000, 01	-.41880000, 02	-.69903000, 04	-.22068600, 05	-.43634132,-02	
.11590000, 01	-.51000000, 02	-.71984000, 04	-.22043520, 05	-.44195152,-02	
.11605000, 01	-.60370000, 02	-.74059800, 04	-.22018740, 05	-.44755702,-02	
.11620000, 01	-.70000000, 02	-.76130600, 04	-.21994270, 05	-.45315802,-02	
.11635000, 01	-.79850000, 02	-.78196300, 04	-.21970070, 05	-.45875462,-02	
.11650000, 01	-.89950000, 02	-.80257000, 04	-.21946200, 05	-.46434663,-02	
.11665000, 01	-.10028000, 03	-.82312700, 04	-.21922620, 05	-.46993433,-02	
.11680000, 01	-.11086000, 03	-.84363300, 04	-.21899320, 05	-.47551743,-02	
.11695000, 01	-.12167000, 03	-.86409000, 04	-.21876310, 05	-.48109623,-02	
.11710000, 01	-.13272000, 03	-.88449900, 04	-.21853610, 05	-.48667083,-02	
.11725000, 01	-.14399000, 03	-.90485800, 04	-.21831180, 05	-.49224093,-02	
.11740000, 01	-.15549000, 03	-.92516800, 04	-.21809040, 05	-.49780683,-02	
.11755000, 01	-.16723000, 03	-.94543000, 04	-.21787180, 05	-.50336850,-02	
.11770000, 01	-.17919000, 03	-.96564400, 04	-.21765610, 05	-.50892590,-02	
.11785000, 01	-.19139000, 03	-.98580900, 04	-.21744320, 05	-.51447900,-02	
.11800000, 01	-.20381000, 03	-.10059280, 05	-.21723300, 05	-.52002810,-02	

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.11800000, 01	-.20383285, 03	.46883448, 03	.71629681, 03	-.52002819,-02	
.13200000, 01	-.13627270, 03	.40127436, 03	.71629681, 03	-.58975259,-02	
.14600000, 01	-.87198481, 02	.35220016, 03	.71629681, 03	-.65875046,-02	
.16000000, 01	-.50433148, 02	.31543483, 03	.71629681, 03	-.72721253,-02	
.17400000, 01	-.22179962, 02	.28718125, 03	.71629670, 03	-.79526810,-02	
.18800000, 01	-.37037037,-04	.26500172, 03	.71629681, 03	-.86300801,-02	

CASE NO. 11

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .11500000, 01 R0 .12000000, 01 E .15000000, 07 NU .35000000, 00

GR-.46000000,-02 GTHETA-.46000000,-02 GZ-.70000000,-02 RG .19000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.10451612, 06 R2-.12750966, 06

AXIAL STRAIN ---.63276730,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.20000000,-01	-.32048800, 04	-.21481730, 05	-.33533950,-02
.11525000, 01	-.73100000, 01	-.35643800, 04	-.21430810, 05	-.34489791,-02
.11550000, 01	-.15400000, 02	-.39223700, 04	-.21380810, 05	-.35444233,-02
.11575000, 01	-.24220000, 02	-.42788600, 04	-.21331720, 05	-.36397295,-02
.11600000, 01	-.33770000, 02	-.46338500, 04	-.21283510, 05	-.37348957,-02
.11625000, 01	-.44050000, 02	-.49873600, 04	-.21236190, 05	-.38299239,-02
.11650000, 01	-.55040000, 02	-.53394200, 04	-.21189760, 05	-.39248191,-02
.11675000, 01	-.66730000, 02	-.56900100, 04	-.21144160, 05	-.40195793,-02
.11700000, 01	-.79120000, 02	-.60391700, 04	-.21099470, 05	-.41142084,-02
.11725000, 01	-.92200000,-02	-.63868900, 04	-.21055600, 05	-.42087046,-02
.11750000, 01	-.10596000, 03	-.67332000, 04	-.21012580, 05	-.43030728,-02
.11775000, 01	-.12040000, 03	-.70781100, 04	-.20970390, 05	-.43973130,-02
.11800000, 01	-.13550000, 03	-.74216200, 04	-.20929020, 05	-.44914262,-02
.11825000, 01	-.15127000, 03	-.77637600, 04	-.20888470, 05	-.45854144,-02
.11850000, 01	-.16769000, 03	-.81045300, 04	-.20848720, 05	-.46792786,-02
.11875000, 01	-.18475000, 03	-.84439500, 04	-.20809770, 05	-.47730208,-02
.11900000, 01	-.20246000, 03	-.87820100, 04	-.20771620, 05	-.48666410,-02
.11925000, 01	-.22080000, 03	-.91187600, 04	-.20734250, 05	-.49601430,-02
.11950000, 01	-.23977000, 03	-.94541800, 04	-.20697650, 05	-.50535260,-02
.11975000, 01	-.25934000, 03	-.97882700, 04	-.20661820, 05	-.51467900,-02
.12000000, 01	-.27955000, 03	-.10121080, 05	-.20626750, 05	-.52399390,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12000000, 01	-.27958211, 03	.65064729, 03	.11383633, 04	-.52399409,-02
.13400000, 01	-.18747099, 03	.55853618, 03	.11383633, 04	-.59623534,-02
.14800000, 01	-.12024048, 03	.49130562, 03	.11383633, 04	-.66748370,-02
.16200000, 01	-.69674333, 02	.44073951, 03	.11383633, 04	-.73799658,-02
.17600000, 01	-.30688111,-02	.40175329, 03	.11363633, 04	-.80794949,-02
.19000000, 01	.21111111,-02	.37106307, 03	.11383633, 04	-.87746621,-02

CASE NO. 12

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3 .1600000, 00

G1 .26785714, 07 G2 .2000000, 06 AA1-.1440000,-02 AA2-.4320000,-01

RI .1150000, 01 RO .1230000, 01 E .1500000, 07 NU .3500000, 00

GR-.4600000,-02 GTHETA-.4600000,-02 GZ-.7000000,-02 RG .1930000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .2000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.59761535,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.2000000,-01	.6025200, 03	-.2050908, 05	-.23406206,-02
.1154000, 01	.1080000, 01	.8930000, 01	-.20413150, 05	-.24972942,-02
.1158000, 01	.8000000,-01	-.5805600, 03	-.20319720, 05	-.26535697,-02
.1162000, 01	-.2930000, 01	-.11660100,-04	-.20226750, 05	-.28094553,-02
.1166000, 01	-.7920000, 01	-.17474800, 04	-.20140210, 05	-.29649578,-02
.1170000, 01	-.1485000, 02	-.23250200, 04	-.20054050, 05	-.31200814,-02
.1174000, 01	-.2370000, 02	-.28986700, 04	-.19970230, 05	-.32748319,-02
.1178000, 01	.3444000, 02	-.34685200, 04	-.19888710, 05	-.34292195,-02
.1182000, 01	-.4702000, 02	-.40345800, 04	-.19809460, 05	-.35832460,-02
.1186000, 01	-.6141000, 02	-.45969400, 04	-.19732440, 05	-.37369206,-02
.1190000, 01	-.7759000, 02	-.51556200, 04	-.19657620, 05	-.38902481,-02
.1194000, 01	-.9554000, 02	-.57107000, 04	-.19584960, 05	-.40432347,-02
.1198000, 01	-.11521000, 03	-.62622100, 04	-.19514420, 05	-.41958872,-02
.1202000, 01	-.13658000, 03	-.68102100, 04	-.19445970, 05	-.43482097,-02
.1206000, 01	-.15962000, 03	-.73547300, 04	-.19379580, 05	-.45002083,-02
.1210000, 01	-.18430000, 03	-.78958300, 04	-.19315220, 05	-.46518880,-02
.1214000, 01	-.21060000, 03	-.84335500, 04	-.19252850, 05	-.48032550,-02
.1218000, 01	-.23847000, 03	-.89679300, 04	-.19192440, 05	-.49543130,-02
.1222000, 01	-.26791000, 03	-.94990400, 04	-.19133960, 05	-.51050710,-02
.1226000, 01	-.29891000, 03	-.10026910, 05	-.19077390, 05	-.52555330,-02
.1230000, 01	-.33139000, 03	-.10551560, 05	-.19022690, 05	-.54057000,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1230000, 01	-.33140781, 03	.78473985, 03	.16944359, 04	-.54057025,-02
.1370000, 01	-.22317670, 03	.67650874, 03	.16944359, 04	-.61544346,-02
.1510000, 01	-.14362903, 04	.59696103, 03	.16944359, 04	-.68914602,-02
.1650000, 01	-.83456925, 02	.53678896, 03	.16944359, 04	-.76197591,-02
.1790000, 01	-.36843148, 02	.49017518, 03	.16944359, 04	-.83413789,-02
.1930000, 01	-.59259259,-03	.45333229, 03	.16944358, 04	-.90577731,-02

CASE NO. 13

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .56000000, 00 RO .59000000, 06 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 G2-.44000000,-02 RG .99000000, 00

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .29000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -40.38823,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.56000000, 00	.40000000,-01	.21969700, 04	-.11978960, 05	-.77151700,-03	
.56150000, 00	.52400000, 01	.17097000, 04	-.11996310, 05	-.83331910,-03	
.56300000, 00	.91400000, 01	.12250600, 04	-.11815250, 05	-.89499620,-03	
.56450000, 00	.11750000, 02	.74302000, 03	-.11735800, 05	-.95654730,-03	
.56600000, 00	.13040000, 02	.26354000, 03	-.11657910, 05	-.10179764,-02	
.56750000, 00	.13060000, 02	.21341000, 03	-.11581570, 05	-.10792865,-02	
.56900000, 00	.11830000, 02	-.68785000, 03	-.11506770, 05	-.11404756,-02	
.57050000, 00	.93800000, 01	-.11597800, 04	-.11433470, 05	-.12015456,-02	
.57200000, 00	.56900000, 01	-.16292800, 04	-.11361670, 05	-.12625017,-02	
.57350000, 00	.82000000, 00	.20963200, 04	-.11291330, 05	-.13233408,-02	
.57500000, 00	-.52700000, 01	-.25609900, 04	-.11222460, 05	-.13840679,-02	
.57650000, 00	-.12530000, 02	-.30232600, 04	-.11155020, 05	-.14446820,-02	
.57800000, 00	-.20920000, 02	-.34831600, 04	-.11089000, 05	-.15051851,-02	
.57950000, 00	-.30490000, 02	-.39407700, 04	-.11024390, 05	-.15655811,-02	
.58100000, 00	-.41170000, 02	-.43960500, 04	-.10961160, 05	-.16258682,-02	
.58250000, 00	-.52980000, 02	-.48496780, 04	-.10899300, 05	-.16860503,-02	
.58400000, 00	-.65860000, 02	-.52998100, 04	-.10838780, 05	-.17461254,-02	
.58550000, 00	-.79840000, 02	-.57483200, 04	-.10779600, 05	-.18060975,-02	
.58700000, 00	-.94910000, 02	-.61946400, 04	-.10721740, 05	-.18659696,-02	
.58850000, 00	-.11103000, 03	-.66387800, 04	-.10665190, 05	-.19257397,-02	
.59000000, 00	-.12818000, 03	-.70807300, 04	-.10609920, 05	-.19854097,-02	

R	SIGMA R	SIGMA THETA	SIGMA Z	U	R
.59000000, 00	-.12821651, 03	.19250420, 04	.11938654, 04	-.19854110,-02	
.67000000, 00	.61612555, 02	.10396633, 04	.94962307, 03	-.26417069,-02	
.75000000, 00	.12805207, 03	.35622272, 03	.73367270, 03	-.32726904,-02	
.83000000, 00	.12269527, 03	-.19282714, 03	.53963036, 03	-.38869680,-02	
.91000000, 00	.74374925, 02	-.64785829, 03	.36345737, 03	-.44900005,-02	
.99000000, 00	-.12962962,-02	-.10343935, 04	.20213833, 03	-.50853934,-02	

CASE NO. 14

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAL-.14400000,-02 AA2-.43200000,-01

RI .56000000, 00 RO .61000000, 00 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .10100000, 01

CL1 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -37908408,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000,-01	.72400000, 04	-.11737170, 05	-.13912430,-03
.56250000, 00	.30340000, 02	.64019800, 04	-.11575800, 05	-.24468090,-03
.56500000, 00	.56680000, 02	.55716500, 04	-.11419240, 05	-.34985260,-03
.56750000, 00	.79160000, 02	.47488800, 04	-.11267970, 05	-.45464720,-03
.57000000, 00	.97860000, 02	.39333560, 04	-.11120080, 05	-.55907190,-03
.57250000, 00	.11284000, 03	.31254800, 04	-.10977910, 05	-.66319750,-03
.57500000, 00	.12419000, 03	.23245800, 04	-.10838950, 05	-.76684810,-03
.57750000, 00	.13200000, 03	.15307100, 04	-.10704900, 05	-.87021180,-03
.58000000, 00	.13633000, 03	.74374000, 03	-.10575090, 05	-.97323640,-03
.58250000, 00	.13725000, 03	.36460000, 02	-.10449430, 05	-.10759291,-02
.58500000, 00	.13487000, 03	-.80997000, 03	-.10327810, 05	-.11782937,-02
.58750000, 00	.12921000, 03	-.15769600, 04	-.10210190, 05	-.12803423,-02
.59000000, 00	.12036000, 03	-.23375200, 04	-.10096460, 05	-.13820790,-02
.59250000, 00	.10841000, 03	-.30917400, 04	-.99865400, 04	-.14835086,-02
.59500000, 00	.93380000, 02	-.38397900, 04	-.98803800, 04	-.15846423,-02
.59750000, 00	.75370000, 02	-.45616900, 04	-.97778600, 04	-.16854799,-02
.60000000, 00	.54430000, 02	-.53176100, 04	-.96789800, 04	-.17860315,-02
.60250000, 00	.30620000, 02	-.60476300, 04	-.95836000, 04	-.18863032,-02
.60500000, 00	.40100000, 01	-.67718600, 04	-.94916800, 04	-.19863008,-02
.60750000, 00	-.25360000, 02	-.74903800, 04	-.94031500, 04	-.20860204,-02
.61000000, 00	-.57420000, 02	-.82033000, 04	-.93179400, 04	-.21854941,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.61000000, 00	-.57433296, 02	.17304904, 04	.14993088, 04	-.21854941,-02
.69000000, 00	.99521814, 02	.89944199, 03	.12633761, 04	-.28416832,-02
.77000000, 00	.14768070, 03	.25122092, 03	.10533543, 04	-.34748259,-02
.85000000, 00	.13192161, 03	-.27371518, 03	.86411107, 03	-.40926517,-02
.93000000, 00	.77669614, 02	-.71148818, 03	.69190296, 03	-.47881198,-02
.10100000, 01	-.32407407,-02	-.10852118, 04	.53391355, 03	-.53005342,-02

CASE NO. 15

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
RI .56000000, 00 RO .64000000, 00 E .15000000, 07 NU .35000000, 00
GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .10400000, 01
C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -34925984,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.00000000, 00	.14023990, 05	-.11480520, 05	.71021620,-03
.56400000, 00	.94500000, 02	.12628770, 05	-.11172230, 05	.53594410,-03
.56800000, 00	.17791700, 03	.11254610, 05	-.10877290, 05	.36277590,-03
.57200000, 00	.25062600, 03	.99008900, 04	-.10595260, 05	.19067680,-03
.57600000, 00	.31301000, 03	.85670700, 04	-.10325700, 05	.19613600,-04
.58000000, 00	.36540000, 03	.72524900, 04	-.10068230, 05	.15045060,-03
.58400000, 00	.40812000, 03	.59566800, 04	-.98224500, 04	.31954170,-03
.58800000, 00	.44150000, 03	.46790500, 04	-.95879800, 04	.48769790,-03
.59200000, 00	.46586000, 03	.34191400, 04	-.93644700, 04	.65494400,-03
.59600000, 00	.48152000, 03	.21764700, 04	-.91515500, 04	.82130920,-03
.60000000, 00	.48871000, 03	.95049000, 03	-.89489200, 04	.98682530,-03
.60400000, 00	.46776000, 03	-.25919000, 03	-.87562400, 04	.11715165,-02
.60800000, 00	.47891000, 03	-.14530100, 04	-.85731900, 04	.13154076,-02
.61200000, 00	.46243000, 03	-.26314000, 04	-.83994700, 04	.14785268,-02
.61600000, 00	.43856000, 03	-.37948100, 04	-.82348200, 04	.16409000,-02
.62000000, 00	.40753000, 03	-.49455900, 04	-.80789400, 04	.18025481,-02
.62400000, 00	.36958000, 03	-.60781500, 04	-.79315600, 04	.1534973,-02
.62800000, 00	.32494000, 03	-.71988500, 04	-.77924300, 04	.21237694,-02
.63200000, 00	.27380000, 03	-.83060600, 04	-.76613000, 04	.22833876,-02
.63600000, 00	.21641000, 03	-.94000600, 04	-.75379200, 04	.24423677,-02
.64000000, 00	.15291000, 03	-.10481280, 05	-.74220600, 04	.26007379,-02
.64000000, 00	.15290385, 03	.12001739, 04	.18346796, 04	.26007383,-02
.72000000, 00	.22767170, 03	.48112281, 03	.16091804, 04	.32456522,-02
.80000000, 00	.22341303, 03	-.90949629, 02	.14074645, 04	.38729369,-02
.88000000, 00	.17279462, 03	-.56168603, 03	.12249904, 04	.44885343,-02
.96000000, 00	.94582222, 02	-.95943288, 03	.10584846, 04	.50963060,-02
.10400000, 01	-.19259259,-02	-.13026894, 04	.90516040, 03	.56988499,-02

CASE NO. 16

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAL-.14400000,-02 AA2-.43200000,-01

R1 .56000000, 00 R0 .59000000, 00 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .12900000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.10451612, 06 R2-.12750966, 06

AXIAL STRAIN -41859201,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000,-01	.46282800, 04	-.13097150, 05	-.49121780,-03
.55150000, 00	.11720000, 02	.41366500, 04	-.13007950, 05	-.55341110,-03
.56300000, 00	.22050000, 02	.36476900, 04	-.12920420, 05	-.61547430,-03
.56450000, 00	.31050000,-02	.31614400, 04	-.12834520, 05	-.67740360,-03
.56600000, 00	.38700000, 02	.26777900, 04	-.12750250, 05	-.73920690,-03
.56750000, 00	.45040000, 02	.21967200, 04	-.12667580, 05	-.80088510,-03
.56900000, 00	.50070000, 02	.17182300, 04	-.12586490, 05	-.86243640,-03
.57050000, 00	.53840000, 02	.12423000, 04	-.12506950, 05	-.92366370,-03
.57200000, 00	.56330000, 02	.76886000, 03	-.12428960, 05	-.98517090,-03
.57350000, 00	.57590000, 02	.29794000, 03	-.12352480, 05	-.10463552,-02
.57500000, 00	.57590000, 02	-.17055000, 03	-.12277520, 05	-.11074225,-02
.57650000, 00	.56400000, 02	-.63658000, 03	-.12204030, 05	-.11683717,-02
.57800000, 00	.53990000, 02	-.11002100, 04	-.12132010, 05	-.12292050,-02
.57950000, 00	.50420000, 02	-.15614700, 04	-.12061430, 05	-.12899253,-02
.58100000, 00	.45660000, 02	-.20203700, 04	-.11902290, 05	-.13505315,-02
.58250000, 00	.39740000, 02	-.24769600, 04	-.11924570, 05	-.14110288,-02
.58400000, 00	.32710000, 02	-.29311700, 04	-.11858210, 05	-.14714111,-02
.58550000, 00	.24520000, 02	-.33831500, 04	-.11793260, 05	-.15316873,-02
.58700000, 00	.15240000, 02	-.38328800, 04	-.11729560, 05	-.15918566,-02
.58850000, 00	.48600000, 01	-.42803600, 04	-.11667410, 05	-.16519219,-02
.59000000, 00	-.66100000, 01	-.47256200, 04	-.11606490, 05	-.17118601,-02
.59000000, 00	-.66198148, 01	.26860702, 04	.12589274, 04	-.17118800,-02
.73000000, 00	.35214877, 03	.11626002, 04	.85128196, 03	-.28511856,-02
.87000000, 00	.39692303, 03	.15810670, 03	.51538022, 03	-.39214956,-02
.10100000, 01	.31085137, 03	-.57202607, 03	.22970870, 03	-.49565562,-02
.11500000, 01	.16756711, 03	-.11388225, 04	.18819555, 02	-.59738111,-02
.12900000, 01	-.86888888,-03	-.15996589, 04	-.23876111, 03	-.69798393,-02

CASE NO. 17

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3-.1600000, 00
G1 .26785714, 07 G2 .2000000, 06 AAL-.1440000,-02 AA2-.4320000,-01
RI .5600000, 00 RO .6100000, 00 E .1500000, 07 NU .3500000, 00
GR-.7600000,-02 GTHETA-.4400000,-02 GZ-.4400000,-02 RG .1310000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .2000000, 06
R1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -40411371,-02

R				U R			
		SIGMA R	SIGMA THETA	SIGMA Z			
.5600000, 00	.3000000,-01	.95825400, 04	-.13238290, 05	.12250090,-03			
.5625000, 00	.4075000, 02	.87396000, 04	-.13066780, 05	.16530900,-04			
.5650000, 00	.7738000, 02	.79045000, 04	-.12900200, 05	-.8904000,-04			
.5675000, 00	.11004000, 03	.70771200, 04	-.12738420, 05	.19421890, 03			
.5700000, 00	.13881000, 03	.62573100, 04	-.12581370, 05	-.29901280,-03			
.5725000, 00	.16374000, 03	.54448900, 04	-.12428930, 05	-.40343480,-03			
.5750000, 00	.18496000, 03	.46397800, 04	-.12281030, 05	-.50748670,-03			
.5775000, 00	.20250000, 03	.38418200, 04	-.12137560, 05	-.61117960,-03			
.5800000, 00	.21647000, 03	.30508800, 04	-.11998430, 05	-.71452050,-03			
.5825000, 00	.22696000, 03	.22668600, 04	-.11633560, 05	-.61751450,-03			
.5850000, 00	.23401000, 03	.14896600, 04	-.11732850, 05	-.92016740,-03			
.5875000, 00	.23772000, 03	.71909000, 03	-.11606230, 05	-.10224913,-02			
.5900000, 00	.23813000, 03	-.44930000, 02	-.11483610, 05	-.11244912,-02			
.5925000, 00	.23535000, 03	-.80249000, 03	-.11364910, 05	-.12261702,-02			
.5950000, 00	.22941000, 03	-.15537600, 04	-.11250050, 05	-.13275421,-02			
.5975000, 00	.22048000, 03	.22987900, 04	-.11138970, 05	-.14286050,-02			
.6000000, 00	.20834000, 03	-.30377100, 04	-.11031580, 05	-.15293699,-02			
.6025000, 00	.19336000, 03	-.37706400, 04	-.10927800, 05	-.16298429,-02			
.6050000, 00	.17547000, 03	-.44976600, 04	-.10827580, 05	-.17300298,-02			
.6075000, 00	.15476000, 03	-.52188500, 04	-.10730820, 05	-.18299337,-02			
.6100000, 00	.13126000, 03	-.59343600, 04	-.10637480, 05	-.19295656,-02			
R				U R			
		SIGMA R	SIGMA THETA	SIGMA Z			
.6100000, 00	.13123040, 03	.23945104, 04	.14240536, 04	-.19295678,-02			
.7500000, 00	.41291607, 03	.98762696, 03	.10284844, 04	-.30584315,-02			
.8900000, 00	.42450511, 03	.39842777, 02	.70081611, 03	-.41260516,-02			
.1030000, 01	.32269314, 03	-.65748451, 03	.42111736, 03	-.51622351,-02			
.1170000, 01	.17154651, 03	.12034727, 04	.17712018, 03	-.61818946,-02			
.1310000, 01	.22592592,-02	-.16501758, 04	-.39266407, 02	-.71931517,-02			

CASE NO. 18

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
RI .56000000, 00 RO .64000000, 00 E .15000000, 7 NU .35000000, 00
GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .13400000, 01
C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
R1-.10451612, 06 R2-.12750966, 06

AXIAL STRAIN---.38385581,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000,-01	.16318760, 05	-.13404480, 05	.95747680,-03
.56400000, 00	.11076000, 03	.14919400, 05	-.13080910, 05	.78292570,-03
.56800000, 00	.21019000, 03	.13541410, 05	-.12770960, 05	.60951150,-03
.57200000, 00	.29866000, 03	.12184190, 05	-.12747180, 05	.43720040,-03
.57600000, 00	.37654000, 03	.10847130, 05	-.12190150, 05	.26595830,-03
.58000000, 00	.44420000, 03	.95296100, 04	-.11918460, 05	.95747200,-04
.58400000, 00	.50198000, 03	.82311300, 04	-.11658700, 05	-.73460900,-04
.58800000, 00	.55019000, 03	.69511100, 04	-.11410510, 05	-.24170100,-03
.59200000, 00	.58918000, 03	.56890500, 04	-.11173500, 05	-.40900220,-03
.59600000, 00	.61922000, 03	.44447000, 04	-.10947320, 05	.57539230,-03
.60000000, 00	.64061000, 03	.32168500, 04	-.10731650, 05	-.74090340,-03
.60400000, 00	.65365000, 03	.20057200, 04	-.10526140, 05	-.90556350,-03
.60800000, 00	.65862000, 03	.81072000, 03	-.10330460, 05	-.10693936,-02
.61200000, 00	.65574000, 03	-.36868000, 03	-.10144350, 05	-.12324257,-02
.61600000, 00	.64530000, 03	-.15328600, 04	-.99674700, 04	-.13946849,-02
.62000000, 00	.62754000, 03	-.26822000, 04	-.97995700, 04	-.15561910,-02
.62400000, 00	.60267000, 03	-.38171500, 04	-.96403500, 04	-.17169741,-02
.62800000, 00	.57095000, 03	-.49380200, 04	-.94895600, 04	-.18770532,-02
.63200000, 00	.53256000, 03	-.60452400, 04	-.93469600, 04	-.20364543,-02
.63600000, 00	.48775000, 03	-.71390700, 04	-.92122800, 04	-.21951924,-02
.64000000, 00	.43670000, 03	-.82199200, 04	-.90852900, 04	-.23532955,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.64000000, 00	.43668477, 03	.18068930, 04	.16274150, 04	-.23532979,-02
.78000000, 00	.56633599, 03	.59511777, 03	.12486716, 04	-.34528702,-02
.92000000, 00	.50341722, 03	-.24496340, 03	.93262166, 03	-.45065139,-02
.10600000, 01	.36105877, 03	-.87744533, 03	.66142755, 03	-.55369564,-02
.12000000, 01	.18618996, 03	.13811460, 04	.42392567, 03	-.65557464,-02
.13400000, 01	.12962962,-02	-.17985797, 04	.21266040, 03	-.75692234,-02

CASE NO. 19

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AAL-.14400000,-02 AA2-.43200000,-01
 RI .11500000, 01 RO .11800000, 01 E .15000000, 07 NU .35000000, 00
 GR-.76000000,-02 GTHEA-.44000000,-02 GZ-.44000000,-02 RG .15800000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 R1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN .40376249,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.20000000,-01	-.38910800, 04	-.11066720, 05	-.31028997,-02
.11515000, 01	-.52000000, 01	-.41206800, 04	-.11034680, 05	-.31631840,-02
.11530000, 01	-.10710000, 02	-.43497100, 04	-.11002990, 05	-.32234183,-02
.11545000, 01	-.16498000, 02	-.45781300, 04	-.10971650, 05	-.32835946,-02
.11560000, 01	-.22560000, 02	-.48060100, 04	-.10940650, 05	-.33437219,-02
.11575000, 01	-.28900000, 02	-.50332900, 04	-.10909990, 05	-.34037922,-02
.11590000, 01	-.35330000, 02	-.52600200, 04	-.10879680, 05	-.34638135,-02
.11605000, 01	-.42430000, 02	-.54861700, 04	-.10849710, 05	-.35237798,-02
.11620000, 01	-.49600000, 02	-.57117600, 04	-.10820060, 05	-.35836951,-02
.11635000, 01	-.57050000, 02	-.59680000, 04	-.10790760, 05	-.36435604,-02
.11650000, 01	-.64760000, 02	-.61612700, 04	-.10761790, 05	-.37033738,-02
.11665000, 01	-.72740000, 02	-.63851900, 04	-.10733150, 05	-.37631371,-02
.11680000, 01	-.80990000, 02	-.66085400, 04	-.10704830, 05	-.38228474,-02
.11695000, 01	-.89510000, 02	-.68313600, 04	-.10676840, 05	-.38825087,-02
.11710000, 01	-.98280000, 02	-.70536400, 04	-.10649190, 05	-.39421220,-02
.11725000, 01	-.10735000, 03	-.72753700, 04	-.10621850, 05	-.40018850,-02
.11740000, 01	-.11643000, 03	-.74965600, 04	-.10594820, 05	-.40611990,-02
.11755000, 01	-.12618000, 03	-.77172100, 04	-.10568120, 05	-.41206640,-02
.11770000, 01	-.13600000, 03	-.79373300, 04	-.10541730, 05	-.41800810,-02
.11785000, 01	-.14607000, 03	-.81569200, 04	-.10515660, 05	-.42394490,-02
.11800000, 01	-.15639000, 03	-.83759700, 04	-.10489900, 05	-.42987690,-02
.11800000, 01	-.15640311, 03	-.84265596, 04	-.98611740, 03	-.42987717,-02
.12600000, 01	-.70358925, 02	-.98169251, 03	-.86252940, 03	-.49522762,-02
.13400000, 01	-.19376259, 02	-.59398318, 03	-.74467507, 03	-.55921518,-02
.14200000, 01	.53547777, 01	.25205698, 03	.63365674, 03	-.62211117,-02
.15000000, 01	.10297951, 02	.52691518, 02	.52872466, 03	.68412683,-02
.15800000, 01	.37037037,-04	-.32661829, 03	.42924625, 03	-.74542867,-02

CASE NO. 20

E1 .45000000, 07 E2 .15000000, 07 NUI .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAI-.14400000,-02 AA2-.43200000,-01

RI .11500000, 01 RO .12000000, 01 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .16000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95045082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.38192209,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
11500000, 01	.20000000,-01	-.95428000, 03	-.10553800, 05	-.23314093,-02
11525000, 01	-.24800000, 01	-.13452800, 04	-.10493480, 05	-.24335728,-02
11550000, 01	-.58000000, 01	-.17346200, 04	-.10434180, 05	-.25355773,-02
11575000, 01	-.99600000, 01	-.21223200, 04	-.10375890, 05	-.26374248,-02
11600000, 01	-.14940000, 02	-.25083300, 04	-.10318600, 05	-.27391143,-02
11625000, 01	-.20710000, 02	-.28927300, 04	-.10262290, 05	-.28406478,-02
11650000, 01	-.27280000, 02	-.32754800, 04	-.10206960, 05	-.29420283,-02
11675000, 01	-.34640000, 02	-.36566500, 04	-.10152610, 05	-.30432568,-02
11700000, 01	-.42800000, 02	-.40362400, 04	-.10092100, 05	-.31443373,-02
11725000, 01	-.51700000, 02	-.44142200, 04	-.10046750, 05	-.32452648,-02
11750000, 01	-.61390000, 02	-.47906600, 04	-.99952400, 04	-.33463483,-02
11775000, 01	-.71630000, 02	-.51655300, 04	-.99446500, 04	-.34466638,-02
11800000, 01	-.83020000, 02	-.55388800, 04	-.98949900, 04	-.35471773,-02
11825000, 01	-.94950000, 02	-.59107000, 04	-.98462300, 04	-.36475279,-02
11850000, 01	-.10760000, 03	-.62610000, 04	-.97983800, 04	-.37477364,-02
11875000, 01	-.12100000, 03	-.66498200, 04	-.97514100, 04	-.38476070,-02
11900000, 01	-.13510000, 03	-.70171500, 04	-.97053300, 04	-.39477400,-02
11925000, 01	-.14990000, 03	-.73830000, 04	-.96601300, 04	-.40475360,-02
11950000, 01	-.16542000, 03	-.77474000, 04	-.96157900, 04	-.41471970,-02
11975000, 01	-.18162000, 03	-.81103400, 04	-.95723000, 04	-.42467230,-02
12000000, 01	-.19852000, 03	-.84718600, 04	-.95296600, 04	-.43461200,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
12000000, 01	-.19852637, 03	.15708910, 04	.13514962, 04	-.43461187,-02
12800000, 01	-.10231092, 03	.11216445, 04	.12279354, 04	-.50110498,-02
13600000, 01	-.42089259, 02	.72980062, 03	.11118676, 04	-.56617904,-02
14400000, 01	-.90023333, 01	.38405222, 03	.10024361, 04	-.63011035,-02
15200000, 01	.34258518, 01	.75872185, 02	.69892296, 03	-.69311493,-02
16000000, 01	.14629629,-02	-.20128229, 03	.80072033, 03	-.75536373,-02

CASE NO. 21

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

RI .11500000, 01 RO .12300000, 01 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHEIA-.44000000,-02 GZ-.44000000,-02 RG .16300000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -0.35348567,-02

R	SIGMA R	SIGMA THEIA	SIGMA Z	U R
.11500000, 01	.10000000,-01	.30017600, 04	-.99071300, 04	-.12939765,-02
.11540000, 01	.93100000, 01	.23584700, 04	-.97958400, 04	-.14610259,-02
.11580000, 01	.16310000, 02	.17196800, 04	-.96873200, 04	-.16276273,-02
.11620000, 01	.21080000, 02	.10853200, 04	-.95815300, 04	-.17937927,-02
.11660000, 01	.23650000, 02	.45535000, 03	-.94784200, 04	-.19595251,-02
.11700000, 01	.24050000, 02	-.17031000, 03	-.93779600, 04	-.21248334,-02
.11740000, 01	.22330000, 02	-.79171000, 03	-.92800800, 04	-.22897228,-02
.11780000, 01	.18520000, 02	-.14089000, 04	-.91847600, 04	-.24542012,-02
.11820000, 01	.12650000, 02	-.20219600, 04	-.90919600, 04	-.26182766,-02
.11860000, 01	.47600000,-01	-.26309200, 04	-.90016200, 04	-.27819520,-02
.11900000, 01	-.51100000, 01	-.32358600, 04	-.89137200, 04	-.29452394,-02
.11940000, 01	-.16950000, 02	-.38368400, 04	-.88282100, 04	-.31081428,-02
.11980000, 01	-.30710000, 02	-.44339100, 04	-.87450600, 04	-.32706702,-02
.12020000, 01	-.46340000, 02	-.50271000, 04	-.86642300, 04	-.34328236,-02
.12060000, 01	-.63840000, 02	-.56164800, 04	-.85856700, 04	-.35946120,-02
.12100000, 01	-.83170000,-02	-.62021000, 04	-.85093700, 04	-.37560438,-02
.12140000, 01	-.10429000, 03	-.67840100, 04	-.84352700, 04	-.39171200,-02
.12180000, 01	-.12717000, 03	-.73622600, 04	-.83633500, 04	-.40778490,-02
.12220000, 01	-.15179000, 03	-.79369000, 04	-.82935600, 04	-.42382380,-02
.12260000, 01	-.17113000, 03	-.85079900, 04	-.82259000, 04	-.43982930,-02
.12300000, 01	-.20614000, 03	-.90755400, 04	-.81602900, 04	-.45580160,-02
R	SIGMA R	SIGMA THEIA	SIGMA Z	U R
.12300000, 01	-.20615792, 03	.15934309, 04	.17832604, 04	-.45580149,-02
.13100000, 01	-.11003281, 03	.11526195, 04	.16626202, 04	-.52319532,-02
.13900000, 01	-.48694777, 02	.76703333, 03	.15491334, 04	-.58918580,-02
.14700000, 01	-.13763037, 02	.42600307, 03	.14419989, 04	-.65404019,-02
.15500000, 01	-.93297036, 00	.12143359, 03	.13405430, 04	-.71796854,-02
.16300000, 01	.13703703,-02	-.15291762, 03	.12441942, 04	-.78113796,-02

CASE NO. 22

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

RI .11500000, 01 RO .11800000, 01 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .18800000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.41853620,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.20000000,-01	-.26596900, 04	-.11928560, 05	-.28234492,-02
.11515000, 01	-.35900000, 01	-.28899400, 04	-.11694970, 05	-.28838432,-02
.11530000, 01	-.75100000, 01	-.31196300, 04	-.11661750, 05	-.29441862,-02
.11545000, 01	-.11690000, 02	-.33487000, 04	-.11828860, 05	-.30044691,-02
.11560000, 01	-.16170000, 02	-.35772100, 04	-.11796330, 05	-.30647021,-02
.11575000, 01	-.20930000, 02	-.38051300, 04	-.11764150, 05	-.31248791,-02
.11590000, 01	-.25990000, 02	-.40324900, 04	-.11732320, 05	-.31850030,-02
.11605000, 01	-.31300000, 02	-.42592600, 04	-.11700820, 05	-.32450720,-02
.11620000, 01	-.36910000, 02	-.44854700, 04	-.11669670, 05	-.33050890,-02
.11635000, 01	-.42790000, 02	-.47111100, 04	-.11638860, 05	-.33650530,-02
.11650000, 01	-.48950000, 02	-.49361800, 04	-.11608390, 05	-.34249649,-02
.11665000, 01	-.55370000, 02	-.51607000, 04	-.11578250, 05	-.34848249,-02
.11680000, 01	-.62070000, 02	-.53846500, 04	-.11548450, 05	-.35446309,-02
.11695000, 01	-.69040000, 02	-.56080500, 04	-.11518980, 05	-.36043878,-02
.11710000, 01	-.76280000, 02	-.58309100, 04	-.11489840, 05	-.36640938,-02
.11725000, 01	-.83780000, 02	-.60592100, 04	-.11461020, 05	-.37237478,-02
.11740000, 01	-.91560000, 02	-.62749800, 04	-.11432540, 05	-.37833537,-02
.11755000, 01	-.99590000, 02	-.64961900, 04	-.11404370, 05	-.38429077,-02
.11770000, 01	-.10788000, 03	-.67168600, 04	-.11376520, 05	-.39024127,-02
.11785000, 01	-.11643000, 03	-.69369900, 04	-.11349000, 05	-.39618667,-02
.11800000, 01	-.12524000, 03	-.71566000, 04	-.11321790, 05	-.40212740,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11800000, 01	-.12525381, 03	.17569305, 04	.89304381, 03	-.40212794,-02
.13200000, 01	.31637259, 02	.98654825, 03	.67839192, 03	-.51585880,-02
.14600000, 01	.92980518, 02	.37399462, 03	.48539833, 03	-.62570127,-02
.16000000, 01	.94899407, 02	-.12860459, 03	.31009018, 03	-.73285877,-02
.17400000, 01	.59412796, 02	-.55215685, 03	.14949659, 03	-.83811190,-02
.18800000, 01	.22222222,-03	-.91605577, 03	.13375555, 01	-.94207100,-02

CASE NO. 23

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .11500000, 01 RC .12000000, 01 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHEIA-.44000000,-02 GZ-.44000000,-02 KG .19000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN - -.40436976,-02

R	SIGMA R	SIGMA THEIA	SIGMA Z	U R
.11500000, 01	.10000000,-01	.16167000, 03	-.11742500, 05	-.20948258,-02
.11525000, 01	-.60000000,-01	-.22937000, 03	-.11679990, 05	-.21969519,-02
.11550000, 01	-.98000000, 00	-.61873000, 03	-.11618520, 05	-.22989161,-02
.11575000, 01	-.27300000, 01	-.10064100, 04	-.11558070, 05	-.24007193,-02
.11600000, 01	-.53100000, 01	-.13924400, 04	-.11498630, 05	-.25023624,-02
.11625000, 01	-.87000000, 01	-.17768000, 04	-.11440190, 05	-.26038456,-02
.11650000, 01	-.12920000, 02	-.21595500, 04	-.11362730, 05	-.27051748,-02
.11675000, 01	-.17920000, 02	-.25406700, 04	-.11326260, 05	-.28063469,-02
.11700000, 01	-.23720000, 02	-.29202200, 04	-.11270750, 05	-.29073701,-02
.11725000, 01	-.30290000, 02	-.32981400, 04	-.11216200, 05	-.30082363,-02
.11750000, 01	-.37650000, 02	-.36745000, 04	-.11162600, 05	-.31089554,-02
.11775000, 01	-.45770000, 02	-.40493000, 04	-.11109940, 05	-.32095256,-02
.11800000, 01	-.54650000, 02	-.44225600, 04	-.11058210, 05	-.33099498,-02
.11825000, 01	-.64270000, 02	-.47942700, 04	-.11007400, 05	-.34102279,-02
.11850000, 01	-.74640000, 02	-.51644600, 04	-.10957500, 05	-.35103611,-02
.11875000, 01	-.85750000, 02	-.55331400, 04	-.10908510, 05	-.36105533,-02
.11900000, 01	-.97580000, 02	-.59003400, 04	-.10860400, 05	-.37102064,-02
.11925000, 01	-.11012000, 03	-.62660500, 04	-.10813180, 05	-.38094196,-02
.11950000, 01	-.12339000, 03	-.66303000, 04	-.10766840, 05	-.39094960,-02
.11975000, 01	-.13735000, 03	-.69930800, 04	-.10721360, 05	-.40089340,-02
.12000000, 01	-.15201000, 03	-.73544200, 04	-.10676740, 05	-.41082390,-02
.12000000, 01	-.15201470, 03	-.76522451, 03	.23162529, 03	-.95586380,-02
.13400000, 01	.10336999, 02	.10345066, 04	.90014885, 03	-.52565193,-02
.14800000, 01	.77331296, 02	.42393640, 03	.70989729, 03	-.63655722,-02
.16200000, 01	.84934759, 02	.76075555, 02	.53685433, 03	-.74473580,-02
.17600000, 01	.54669740, 02	.50123314, 03	.37616348, 03	-.85898110,-02
.19000000, 01	.72222222,-03	-.86522451, 03	.23162529, 03	-.95586380,-02

CASE NO. 24

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAI-.14400000,-02 AA2-.43200000,-01

RI .11500000, 01 RO .12300000, 01 E .15000000, 07 NU .35000000, 00

GR-.76000000,-02 GTHETA-.44000000,-02 GZ-.44000000,-02 RG .19300000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.38431312,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.20000000,-01	.40417100, 04	-.11460740, 05	-.10917414,-02
.11540000, 01	.12920000, 02	.34000400, 04	-.11346470, 05	-.12583780,-02
.11580000, 01	.23530000, 02	.27629200, 04	-.11234990, 05	-.14245585,-02
.11620000, 01	.31860000, 02	.21302300, 04	-.11126250, 05	-.15902980,-02
.11660000, 01	.37980000, 02	.15019500, 04	-.11020220, 05	-.17555995,-02
.11700000, 01	.41920000, 02	.87799000, 03	-.10916850, 05	-.19204711,-02
.11740000, 01	.43710000, 02	.25832000, 03	-.10816090, 05	-.20849166,-02
.11780000, 01	.43400000, 02	-.35713000, 03	-.10717900, 05	-.22489461,-02
.11820000, 01	.41000000, 02	-.96843000, 03	-.10622240, 05	-.24125666,-02
.11860000, 01	.36570000, 02	-.15756400, 04	-.10529080, 05	-.25757842,-02
.11900000, 01	.30140000, 02	-.21788100, 04	-.10438360, 05	-.27386057,-02
.11940000, 01	.21730000, 02	-.27779900, 04	-.10350050, 05	-.29010382,-02
.11980000, 01	.11380000, 02	-.33732500, 04	-.10264120, 05	-.30630887,-02
.12020000, 01	-.86000000, 00	-.39646200, 04	-.10180530, 05	-.32247613,-02
.12060000, 01	-.14980000, 02	-.45521700, 04	-.10099230, 05	-.33860628,-02
.12100000, 01	-.30950000, 02	-.51359500, 04	-.10020200, 05	-.35470613,-02
.12140000, 01	-.48730000, 02	-.57160000, 04	-.99433900, 04	-.37075810,-02
.12180000, 01	-.68290000, 02	-.62923700, 04	-.98667600, 04	-.38678070,-02
.12220000, 01	-.89590000, 02	-.68651300, 04	-.97963000, 04	-.40276870,-02
.12260000, 01	-.11263000, 03	-.74343300, 04	-.97259700, 04	-.41872300,-02
.12300000, 01	-.13736000, 03	-.79999700, 04	-.96577200, 04	-.43464340,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12300000, 01	-.13739085, 03	.17400618, 04	.13962380, 04	-.43464383,-02
.13700000, 01	.15047074, 02	.99796718, 03	.11898582, 04	-.55016912,-02
.15100000, 01	.77662222, 02	.40311874, 03	.10035765, 04	-.66191502,-02
.16500000, 01	.83820240, 02	-.88047444, 02	.83382370, 03	-.77101451,-02
.17900000, 01	.53709388, 02	-.50342248, 03	.67798362, 03	-.87623210,-02
.19300000, 01	.18703703,-02	-.86163648, 03	.53373111, 03	-.98409960,-02

AFRPL-TR-65-57

APPENDIX D

Calculated Stresses in Composite Cylinders with Pyrolytic Graphite Coating on the Outside

NOTE: See Appendix F for definitions of symbols used in this Appendix.

AFRPL-TR-65-57

APPENDIX D

PHYSICAL PROPERTIES INPUT DATA

Pyrolytic Graphite:*	Young's Modulus	$E_a = 4.5 \times 10^6 \text{ psi}$
	Young's Modulus	$E_c = 1.5 \times 10^6 \text{ psi}$
	Poisson's Ratio	$\nu_{ac} = 0.90$
	Poisson's Ratio	$\nu_{ca} = 0.30$
	Poisson's Ratio	$\nu_{aa} = -0.16$
	Shear Modulus	$G_a = 0.2 \times 10^6 \text{ psi}$
	Shear Modulus	$G_c = 2.68 \times 10^6 \text{ psi}$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.00144 \text{ in/in}$
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0432 \text{ in/in}$
Molded Graphite:**	Young's Modulus	$E = 1.5 \times 10^6 \text{ psi}$
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.0046 \text{ in/in}$
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0070 \text{ in/in}$

* Reference 7.

** Reference 9.

CASE NO. 1

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .16300000, 01 RO .16000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .15000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN -.38901551,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16300000, 01	.30000000,-01	-.16313130, 05	-.84155700, 04	-.87439180,-02
.16285000, 01	.14990000, 02	-.16161580, 05	-.84263600, 04	-.86865230,-02
.16270000, 01	.29830000, 02	-.16009790, 05	-.84372900, 04	-.86291010,-02
.16255000, 01	.44560000, 02	-.15857740, 05	-.84483600, 04	-.85716510,-02
.16240000, 01	.59180000, 02	-.15705440, 05	-.84595700, 04	-.85141740,-02
.16225000, 01	.73690000, 02	-.15552890, 05	-.84709200, 04	-.84566680,-02
.16210000, 01	.88080000, 02	-.15400090, 05	-.84824200, 04	-.83991350,-02
.16195000, 01	.10235000, 03	-.15247040, 05	-.84940600, 04	-.83415760,-02
.16180000, 01	.11650000, 03	-.15093720, 05	-.85058500, 04	-.82839850,-02
.16165000, 01	.13055000, 03	-.14940150, 05	-.85177800, 04	-.82263660,-02
.16150000, 01	.14448000, 03	-.14786340, 05	-.85298600, 04	-.81687210,-02
.16135000, 01	.15828000, 03	-.14632260, 05	-.85420800, 04	-.81110460,-02
.16120000, 01	.17197000, 03	-.14477920, 05	-.85544500, 04	-.80533410,-02
.16105000, 01	.18554000, 03	-.14323330, 05	-.85669700, 04	-.79956100,-02
.16090000, 01	.19900000, 03	-.14168480, 05	-.85796400, 04	-.79378490,-02
.16075000, 01	.21233000, 03	-.14013360, 05	-.85924600, 04	-.78800550,-02
.16060000, 01	.22556000, 03	-.13857980, 05	-.86054300, 04	-.78222340,-02
.16045000, 01	.23864000, 03	-.13702350, 05	-.86185500, 04	-.77643850,-02
.16030000, 01	.25162000, 03	-.13546440, 05	-.86318100, 04	-.77065050,-02
.16015000, 01	.26445000, 03	-.13390270, 05	-.86452400, 04	-.76485950,-02
.16000000, 01	.27714000, 03	-.13233840, 05	-.86588200, 04	-.75906560,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16000000, 01	.27716111, 03	.44300659, 04	.27122968, 04	-.75906608,-02
.15800000, 01	.22458740, 03	.44310340, 04	.26942348, 04	-.74687163,-02
.15600000, 01	.17064851, 03	.44327103, 04	.26759429, 04	-.73461405,-02
.15400000, 01	.11527759, 03	.44351399, 04	.26574149, 04	-.72229125,-02
.15200000, 01	.58421001, 02	.44383714, 04	.26386448, 04	-.70990100,-02
.15000000, 01	-.37037097,-02	.44424574, 04	.26196260, 04	-.69744103,-02

CASE NO. 2

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .16500000, 01 RO .16000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .15000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06
 AXIAL STRAIN --.35360508,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16500000, 01	.40000000,-01	-.14881810, 05	-.70511100, 04	-.82463420,-02
.16475000, 01	.22420000, 02	-.14627350, 05	-.70716700, 04	-.81492680,-02
.16450000, 01	.44490000, 02	-.14372190, 05	-.70926300, 04	-.80521160,-02
.16425000, 01	.66250000, 02	-.14116330, 05	-.71143000, 04	-.79548810,-02
.16400000, 01	.87670000, 02	-.13859760, 05	-.71357600, 04	-.78575650,-02
.16375000, 01	.10876000, 03	-.13602490, 05	-.71579400, 04	-.77601690,-02
.16350000, 01	.12953000, 03	-.13344500, 05	-.71805300, 04	-.76626900,-02
.16325000, 01	.14996000, 03	-.13085790, 05	-.72035300, 04	-.75651260,-02
.16300000, 01	.17007000, 03	-.12826360, 05	-.72269500, 04	-.74674780,-02
.16275000, 01	.18983000, 03	-.12566190, 05	-.72507800, 04	-.73697450,-02
.16250000, 01	.20925000, 03	-.12305310, 05	-.72750500, 04	-.72719290,-02
.16225000, 01	.22834000, 03	-.12043670, 05	-.72997400, 04	-.71740240,-02
.16200000, 01	.24707000, 03	-.11781290, 05	-.73248500, 04	-.70760320,-02
.16175000, 01	.26546000, 03	-.11518180, 05	-.73504100, 04	-.69779540,-02
.16150000, 01	.28349000, 03	-.11254300, 05	-.73763900, 04	-.68797850,-02
.16125000, 01	.30118000, 03	-.10989670, 05	-.74028100, 04	-.67815260,-02
.16100000, 01	.31851000, 03	-.10724280, 05	-.74296800, 04	-.66831800,-02
.16075000, 01	.33547000, 03	-.10458130, 05	-.74570000, 04	-.65847430,-02
.16050000, 01	.35208000, 03	-.10191210, 05	-.74847600, 04	-.64862140,-02
.16025000, 01	.36831000, 03	-.99235100, 04	-.75129800, 04	-.63875930,-02
.16000000, 01	.38418000, 03	-.96550400, 04	-.75416600, 04	-.62888800,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16000000, 01	.38416259, 03	.60903274, 04	.38619951, 04	-.62888830,-02
.15800000, 01	.31180296, 03	.61110818, 04	.38439333, 04	-.61550752,-02
.15600000, 01	.23731222, 03	.61333096, 04	.38256414, 04	-.60202729,-02
.15400000, 01	.16058777, 03	.61570970, 04	.38071133, 04	-.58844413,-02
.15200000, 01	.81521481, 02	.61825348, 04	.37883433, 04	-.57475434,-02
.15000000, 01	-.48148148,-02	.62097211, 04	.37693244, 04	-.56095404,-02

CASE NO. 3

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 -.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 R1 .16800000, 01 R0 .16000000, 01 E .15000000, 07 NU .39000000, 00
 GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .15000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.31740794,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	R	SIGMA R	SIGMA THETA	SIGMA Z	U
.16800000, 01	.10000000,-01	-.14185460, 05	-.55336700, 04	-.80456590,-02	.16000000, 01	.50054629, 03	.78961511, 04	.50777248, 04	-.48599933,-02
.16760000, 01	.33380000, 02	-.13779390, 05	-.55686100, 04	-.78885300,-02	.15800000, 01	.40666592, 03	.79384262, 04	.50596629, 04	-.47134442,-02
.16720000, 01	.65950000, 02	-.13371540, 05	-.56045600, 04	-.77311900,-02	.15600000, 01	.30982148, 03	.79833007, 04	.50413711, 04	-.45655059,-02
.16680000, 01	.97680000, 02	-.12961920, 05	-.56415400, 04	-.75736420,-02	.15400000, 01	.20986703, 03	.80300251, 04	.50228429, 04	-.44161280,-02
.16640000, 01	.12857000, 03	-.12550500, 05	-.56795600, 04	-.74158770,-02	.15200000, 01	.10664703, 03	.80796162, 04	.50040729, 04	-.42652575,-02
.16600000, 01	.15862000, 03	-.12137260, 05	-.57186300, 04	-.72578960,-02	.15000000, 01	-.48148148,-02	.81319285, 04	.49850540, 04	-.41128384,-02
.16560000, 01	.18782000, 03	-.11722190, 05	-.57587600, 04	-.70996930,-02					
.16520000, 01	.21617000, 03	-.11305250, 05	-.57999600, 04	-.69412650,-02					
.16480000, 01	.24362000, 03	-.10886450, 05	-.58422600, 04	-.67826120,-02					
.16440000, 01	.27019000, 03	-.10465750, 05	-.58856600, 04	-.66237250,-02					
.16400000, 01	.29586000, 03	-.10043150, 05	-.59301700, 04	-.64646130,-02					
.16360000, 01	.32062000, 03	-.96186300, 04	-.59758200, 04	-.63052630,-02					
.16320000, 01	.34446000, 03	-.91921600, 04	-.60226000, 04	-.61456750,-02					
.16280000, 01	.36736000, 03	-.87637100, 04	-.60705300, 04	-.59858430,-02					
.16240000, 01	.38933000, 03	-.83333280, 04	-.61196300, 04	-.58257660,-02					
.16200000, 01	.41032000, 03	-.79008500, 04	-.61699200, 04	-.56654440,-02					
.16160000, 01	.43036000, 03	-.74663900, 04	-.62214100, 04	-.55048690,-02					
.16120000, 01	.44941000, 03	-.70298800, 04	-.62741000, 04	-.53440380,-02					
.16080000, 01	.46748000, 03	-.65913000, 04	-.63280200, 04	-.51829500,-02					
.16040000, 01	.48452000, 03	-.61506400, 04	-.63831800, 04	-.50216020,-02					
.16000000, 01	.50056000, 03	-.57078600, 04	-.64395900, 04	-.48599880,-02					

CASE NO. 4

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAL-.14400000,-02 AA2-.43200000,-01

RI .16300000, C1 RO .16000000, 01 E .15000000, 07 NU .35000000, 00

GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .12000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.44290662,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16300000, 01	.10000000,-01	-.21804760, 05	-.99620300, 04	-.10822729,-01
.16285000, 01	.20020000, 02	-.21660710, 05	-.99670600, 04	-.10767449,-01
.16270000, 01	.39950000, 02	-.21516430, 05	-.99722200, 04	-.10712146,-01
.16255000, 01	.59780000, 02	-.21371920, 05	-.99774900, 04	-.10656822,-01
.16240000, 01	.79500000, 02	-.21227190, 05	-.99828900, 04	-.10601475,-01
.16225000, 01	.99130000, 02	-.21082240, 05	-.99864200, 04	-.10546108,-01
.16210000, 01	.11866000, 03	-.20937060, 05	-.99940700, 04	-.10490718,-01
.16195000, 01	.13810000, 03	-.20791640, 05	-.99998500, 04	-.10435304,-01
.16180000, 01	.15743000, 03	-.20645990, 05	-.10005750, 05	-.10379867,-01
.16165000, 01	.17667000, 03	-.20500110, 05	-.10011770, 05	-.10324408,-01
.16150000, 01	.19580000, 03	-.20354010, 05	-.10017930, 05	-.10268927,-01
.16135000, 01	.21484000, 03	-.20207680, 05	-.10024210, 05	-.10213423,-01
.16120000, 01	.23378000, 03	-.20061100, 05	-.10030620, 05	-.10157896,-01
.16105000, 01	.25261000, 03	-.19914310, 05	-.10037160, 05	-.10102347,-01
.16090000, 01	.27134000, 03	-.19767270, 05	-.10043820, 05	-.10046774,-01
.16075000, 01	.28998000, 03	-.19619990, 05	-.10050620, 05	-.99911750,-02
.16060000, 01	.30850000, 03	-.19472480, 05	-.10057550, 05	-.99355540,-02
.16045000, 01	.32692000, 03	-.19324740, 05	-.10064610, 05	-.98799100,-02
.16030000, 01	.34524000, 03	-.19176760, 05	-.10071790, 05	-.98242430,-02
.16015000, 01	.36345000, 03	-.19028540, 05	-.10079120, 05	-.97685500,-02
.16000000, 01	.38156000, 03	-.18880080, 05	-.10086570, 05	-.97128350,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16000000, 01	.38156436, 03	.18965740, 04	.10537491, 04	-.97128381,-02
.15200000, 01	.30531496, 03	.17623892, 04	.98009718, 03	-.93100050,-02
.14400000, 01	.22833625, 03	.16175535, 04	.90246214, 03	-.89070968,-02
.13600000, 01	.15117870, 03	.14602152, 04	.82038855, 03	-.85043822,-02
.12800000, 01	.74660518, 02	.12880167, 04	.73333774, 03	-.81022144,-02
.12000000, 01	-.23703703,-02	.10979062, 04	.64066707, 03	-.77010609,-02

CASE NO. 5

E1 .4500000, 07 E2 .1500000, 07 NU1 .3000000, 00 NU2 .9000000, 00 NU3-.1600000, 00

G1 .26785714, 07 G2 .2000000, 06 AA1-.1400000,-02 AA2-.4320000,-01

RI .1650000, 01 RO .1600000, 01 E .1500000, 07 NU .3500000, 00

GR-.4600000,-02 GTHETA-.7000000,-02 GZ-.4600000,-02 RG .1200000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .2000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.43250529,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1650000, 01	.2000000,-01	-.21949840, 05	-.94707400, 04	-.10979900,-01
.16475000, 01	.33160000, 02	-.21711970, 05	-.94789800, 04	-.10887578,-01
.16450000, 01	.66020000, 02	-.21473510, 05	-.94875500, 04	-.10795201,-01
.16425000, 01	.98620000, 02	-.21234430, 05	-.94964700, 04	-.10702761,-01
.16400000, 01	.13096000, 03	-.20994730, 05	-.95057100, 04	-.10610259,-01
.16375000, 01	.16303000, 03	-.20754420, 05	-.95153300, 04	-.10517698,-01
.16350000, 01	.19483000, 03	-.20513470, 05	-.95252300, 04	-.10425072,-01
.16325000, 01	.22636000, 03	-.20271900, 05	-.95355100, 04	-.10332386,-01
.16300000, 01	.25761000, 03	-.20029690, 05	-.95461300, 04	-.10239634,-01
.16275000, 01	.28859000, 03	-.19786850, 05	-.95571100, 04	-.10146819,-01
.16250000, 01	.31928000, 03	-.19543370, 05	-.95684400, 04	-.10053394,-01
.16225000, 01	.34970000, 03	-.19299240, 05	-.95801200, 04	-.99609950,-02
.16200000, 01	.37983000, 03	-.19054460, 05	-.95921700, 04	-.98679850,-02
.16175000, 01	.40969000, 03	-.18809040, 05	-.96045700, 04	-.97749090,-02
.16150000, 01	.43924000, 03	-.18562950, 05	-.96173400, 04	-.96817640,-02
.16125000, 01	.46851000, 03	-.18316200, 05	-.96304800, 04	-.95885510,-02
.16100000, 01	.49749000, 03	-.18066600, 05	-.96439900, 04	-.94952720,-02
.16075000, 01	.52618000, 03	-.17820710, 05	-.96578600, 04	-.94019220,-02
.16050000, 01	.55456000, 03	-.17571960, 05	-.96721200, 04	-.93085040,-02
.16025000, 01	.58264000, 03	-.17322540, 05	-.96867500, 04	-.92150170,-02
.16000000, 01	.61042000, 03	-.17072430, 05	-.97017700, 04	-.91214570,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1600000, 01	.61039962, 03	.27138450, 04	.15759062, 04	-.91214528,-02
.1520000, 01	.50236492, 03	.26114457, 04	.15022543, 04	-.87047067,-02
.1450000, 01	.38015755, 03	.25038386, 04	.14246192, 04	-.82854076,-02
.1360000, 01	.26700985, 03	.23904504, 04	.13425457, 04	-.78633877,-02
.1280000, 01	.13799811, 03	.22707854, 04	.12554948, 04	-.74384530,-02
.1200000, 01	-.32962962,-02	.21440135, 04	.11626242, 04	-.70103789,-02

CASE NO. 6

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .16800000, 01 RO .16000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.46000000,-02 GTHEA-.70000000,-02 GZ-.46000000,-02 RG .12000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.41878607,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16800000, 01	.20000000,-01	-.22362600, 05	-.87873400, 04	-.11292809,-01
.16760000, 01	.52940000, 02	-.21987940, 05	-.87996600, 04	-.11144854,-01
.16720000, 01	.10522000, 03	-.21611760, 05	-.86127900, 04	-.10996749,-01
.16680000, 01	.15685000, 03	-.21234070, 05	-.88267600, 04	-.10848493,-01
.16640000, 01	.20781000, 03	-.20854830, 05	-.88415700, 04	-.10700083,-01
.16600000, 01	.25811000, 03	-.20474050, 05	-.88572300, 04	-.10551516,-01
.16560000, 01	.30772000, 03	-.20091700, 05	-.88737500, 04	-.10402790,-01
.16520000, 01	.35666000, 03	-.19707750, 05	-.88911500, 04	-.10253900,-01
.16480000, 01	.40489000, 03	-.19322220, 05	-.89094300, 04	-.10104849,-01
.16440000, 01	.45241000, 03	-.18935060, 05	-.89285900, 04	-.99556290,-02
.16400000, 01	.49922000, 03	-.18546270, 05	-.89486700, 04	-.98062410,-02
.16360000, 01	.54531000, 03	-.18155850, 05	-.89696600, 04	-.96566830,-02
.16320000, 01	.59067000, 03	-.17763760, 05	-.89915700, 04	-.95069510,-02
.16280000, 01	.63528000, 03	-.17369990, 05	-.90144200, 04	-.93570410,-02
.16240000, 01	.67915000, 03	-.16974520, 05	-.90382200, 04	-.92069510,-02
.16200000, 01	.72224000, 03	-.16577350, 05	-.90629800, 04	-.90566830,-02
.16160000, 01	.76457000, 03	-.16178450, 05	-.90887100, 04	-.89062300,-02
.16120000, 01	.80612000, 03	-.15777790, 05	-.91154200, 04	-.87555870,-02
.16080000, 01	.84687000, 03	-.15375380, 05	-.91431300, 04	-.86047550,-02
.16040000, 01	.88682000, 03	-.14971190, 05	-.91718500, 04	-.84537330,-02
.16000000, 01	.92596000, 03	-.14565200, 05	-.92015800, 04	-.83025150,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.16000000, 01	.92593636, 03	.38407651, 04	.22865544, 04	-.83025137,-02
.15200000, 01	.77407344, 03	.37821940, 04	.22129025, 04	-.78667576,-02
.14400000, 01	.60853203, 03	.37259211, 04	.21352674, 04	-.74250324,-02
.13600000, 01	.42672736, 03	.36732296, 04	.20531938, 04	-.69765667,-02
.12800000, 01	.22533340, 03	.36259070, 04	.19661430, 04	-.65204136,-02
.12000000, 01	-.44444444,-02	.35864714, 04	.18734724, 04	-.60553936,-02

CASE NO. 7

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

R1 .32300000, 01 R0 .32000000, 01 E .15000000, 07 NU .35000000, 00

GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .31000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.1C451612, 06 B2-.12750966, 06

AXIAL STRAIN --.38685602,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32300000, 01	.50000000,-01	-.15102800, 05	-.85120300, 04	-.16469246,-01
.32285000, 01	.70400000, 01	-.15025750, 05	-.85180600, 04	-.16411531,-01
.32270000, 01	.14010000, 02	-.14948630, 05	-.85241300, 04	-.16353793,-01
.32255000, 01	.20970000, 02	-.14871420, 05	-.85302300, 04	-.16296035,-01
.32240000, 01	.27870000, 02	-.14794180, 05	-.85363700, 04	-.16238273,-01
.32225000, 01	.34760000, 02	-.14716850, 05	-.85425500, 04	-.16180490,-01
.32210000, 01	.41610000, 02	-.14639470, 05	-.85487600, 04	-.16122269,-01
.32195000, 01	.48410000, 02	-.14562040, 05	-.85550200, 04	-.16064889,-01
.32180000, 01	.55220000, 02	-.14484510, 05	-.85613100, 04	-.16007059,-01
.32165000, 01	.61980000, 02	-.14406950, 05	-.85676300, 04	-.15949230,-01
.32150000, 01	.68700000, 02	-.14329300, 05	-.85740000, 04	-.15891373,-01
.32135000, 01	.75420000, 02	-.14251580, 05	-.85803900, 04	-.15833502,-01
.32120000, 01	.82100000, 02	-.14173790, 05	-.85868300, 04	-.15775613,-01
.32105000, 01	.88730000, 02	-.14095970, 05	-.85933100, 04	-.15717725,-01
.32090000, 01	.95340000, 02	-.14018070, 05	-.85998200, 04	-.15659812,-01
.32075000, 01	.10191000, 03	-.13940110, 05	-.86063800, 04	-.15601889,-01
.32060000, 01	.10847000, 03	-.13862050, 05	-.86129600, 04	-.15543943,-01
.32045000, 01	.11500000, 03	-.13783950, 05	-.86195900, 04	-.15485986,-01
.32030000, 01	.12148000, 03	-.13705790, 05	-.86262600, 04	-.15428017,-01
.32015000, 01	.12794000, 03	-.13627560, 05	-.86329700, 04	-.15370034,-01
.32000000, 01	.13437000, 03	-.13549270, 05	-.86397100, 04	-.15312040,-01
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32000000, 01	.13430444, 03	.42962229, 04	.26478443, 04	-.15312062,-01
.31800000, 01	.10812740, 03	.42966785, 04	.26388417, 04	-.15189293,-01
.31600000, 01	.81615925, 02	.42973066, 04	.26297825, 04	-.15066212,-01
.31400000, 01	.54761851, 02	.42981122, 04	.26206657, 04	-.14942815,-01
.31200000, 01	.27557777, 02	.42991022, 04	.26114906, 04	-.14819095,-01
.31000000, 01	-.44444444,-02	.43002807, 04	.26022564, 04	-.14695049,-01

CASE NO. 8

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 RI .32500000, 01 RO .32000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .31000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.34954433,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.3250000, 01	.1000000,-01	-.13003610, 05	-.71689000, 04	-.14899912,-01
.32475000, 01	.99700000, 01	-.12872920, 05	-.71808500, 04	-.14801982,-01
.32450000, 01	.19850000, 02	-.12742020, 05	-.71929000, 04	-.14704001,-01
.32425000, 01	.29630000, 02	-.12610970, 05	-.72050700, 04	-.14605985,-01
.32400000, 01	.39340000, 02	-.12479710, 05	-.72173400, 04	-.14507921,-01
.32375000, 01	.48950000, 02	-.12348280, 05	-.72297200, 04	-.14409815,-01
.32350000, 01	.58490000, 02	-.12216650, 05	-.72422000, 04	-.14311665,-01
.32325000, 01	.67920000, 02	-.12084840, 05	-.72548000, 04	-.14213472,-01
.32300000, 01	.77290000, 02	-.11952810, 05	-.72674900, 04	-.14115221,-01
.32275000, 01	.86560000, 02	-.11820620, 05	-.72802900, 04	-.14016940,-01
.32250000, 01	.95730000, 02	-.11688250, 05	-.72932200, 04	-.13918615,-01
.32225000, 01	.10482000, 03	-.11555680, 05	-.73062250, 04	-.13820243,-01
.32200000, 01	.11382000, 03	-.11422920, 05	-.73193900, 04	-.13721826,-01
.32175000, 01	.12273000, 03	-.11289970, 05	-.73326400, 04	-.13623365,-01
.32150000, 01	.13156000, 03	-.11156830, 05	-.73460000, 04	-.13524859,-01
.32125000, 01	.14029000, 03	-.11023510, 05	-.73594700, 04	-.13426312,-01
.32100000, 01	.14893000, 03	-.10889970, 05	-.73730600, 04	-.13327706,-01
.32075000, 01	.15748000, 03	-.10756260, 05	-.73867600, 04	-.13229067,-01
.32050000, 01	.16595000, 03	-.10622340, 05	-.74005700, 04	-.13130374,-01
.32025000, 01	.17431000, 03	-.10488240, 05	-.74144900, 04	-.13031643,-01
.32000000, 01	.18259000, 03	-.10353960, 05	-.74285400, 04	-.12932870,-01
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.3200000, 01	.18255148, 03	.58163648, 04	.37564555, 04	-.12932880,-01
.31800000, 01	.14708814, 03	.58261066, 04	.37474529, 04	-.12798404,-01
.31600000, 01	.11111370, 03	.58361981, 04	.37383936, 04	-.12663447,-01
.31400000, 01	.74614814, 02	.58466485, 04	.37292770, 04	-.12528001,-01
.31200000, 01	.37580370, 02	.58574685, 04	.37201018, 04	-.12392058,-01
.31000000, 01	-.33333333,-02	.58686688, 04	.37108677, 04	-.12255610,-01

CASE NO. 9

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01
 R1 .32800000, 01 R0 .32000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.46000000,-02 GTHETA-.70000000,-02 GZ-.46000000,-02 RG .31000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.31105917,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32800000, 01	.30000000,-01	-.11420470, 05	-.56903500, 04	-.13711105,-01
.32760000, 01	.13860000, 02	-.11208920, 05	-.57117600, 04	-.13551925,-01
.32720000, 01	.27440000, 02	-.10996940, 05	-.57334600, 04	-.13392654,-01
.32680000, 01	.40820000, 02	-.10784410, 05	-.57554200, 04	-.13233238,-01
.32640000, 01	.53940000, 02	-.10571460, 05	-.57776800, 04	-.13073730,-01
.32600000, 01	.66860000, 02	-.10357960, 05	-.58002000, 04	-.12914080,-01
.32560000, 01	.79530000, 02	-.10144040, 05	-.58230400, 04	-.12754336,-01
.32520000, 01	.91970000, 02	-.99295900, 04	-.58461500, 04	-.12594461,-01
.32480000, 01	.10418000, 03	-.97146600, 04	-.58695500, 04	-.12434472,-01
.32440000, 01	.11615000, 03	-.94992400, 04	-.58932250, 04	-.12274356,-01
.32400000, 01	.12789000, 03	-.92833000, 04	-.59172300, 04	-.12114117,-01
.32360000, 01	.13938000, 03	-.90668800, 04	-.59415200, 04	-.11953767,-01
.32320000, 01	.15065000, 03	-.88499100, 04	-.59660800, 04	-.11793271,-01
.32280000, 01	.16168000, 03	-.86324600, 04	-.59909600, 04	-.11632660,-01
.32240000, 01	.17244000, 03	-.84145300, 04	-.60161400, 04	-.11471934,-01
.32200000, 01	.18297000, 03	-.81960600, 04	-.60416100, 04	-.11311073,-01
.32160000, 01	.19327000, 03	-.79770700, 04	-.60673900, 04	-.11150085,-01
.32120000, 01	.20331000, 03	-.77575500, 04	-.60934700, 04	-.10988965,-01
.32080000, 01	.21309000, 03	-.75375500, 04	-.61198600, 04	-.10827727,-01
.32040000, 01	.22262000, 03	-.73170300, 04	-.61465700, 04	-.10666363,-01
.32000000, 01	.23190000, 03	-.70959800, 04	-.61735900, 04	-.10504873,-01
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32000000, 01	.23186925, 03	.73701803, 04	.48948296, 04	-.10504883,-01
.31800000, 01	.18691370, 03	.73894140, 04	.48858270, 04	-.10358416,-01
.31600000, 01	.14126629, 03	.74091781, 04	.48767677, 04	-.10211296,-01
.31400000, 01	.94909629, 02	.74294866, 04	.48676511, 04	-.10063510,-01
.31200000, 01	.47826296, 02	.74503555, 04	.48584759, 04	-.99150490,-02
.31000000, 01	-.74074074,-03	.74717992, 04	.48492418, 04	-.97658990,-02

CASE NO. 10														
E1	.45000000	.07	E2	.15000000	.07	NU1	.30000000	.00	NU2	.90000000	.00	NU3	.16000000	.00
G1	.26785714	.07	G2	.20000000	.06	AA1	.14400000	-.02	AA2	.43200000	-.01			
R1	.32300000	.01	R0	.32000000	.01	E	.15000000	.07	NU	.35000000	.00			
GR	.46000000	-.02	GTHETA	-.70000000	-.02	GZ	-.46000000	-.02	RG	.28000000	.01			
C11	.63076036	.07	C12	.21774193	.07	C13	.95046082	.06	C22	.28064516	.07	C44	.20000000	.06
B1	.10451612	.06	B2	.12750966	.06									
AXIAL STRAIN					-.44302965, -.02									
R														
.32300000	.01	.40000000	-.01	-.20806790	.05	-.10127210	.05	-.20748935	-.01					
.32250000	.01	.96800000	.01	-.20733680	.05	-.10130230	.05	-.20693418	-.01					
.32270000	.01	.19310000	.02	-.20660490	.05	-.10133280	.05	-.20637679	-.01					
.32255000	.01	.28910000	.02	-.20587230	.05	-.10136360	.05	-.20582325	-.01					
.32240000	.01	.38480000	.02	-.20513930	.05	-.10139470	.05	-.20526770	-.01					
.32225000	.01	.48040000	.02	-.20440560	.05	-.10142610	.05	-.20471195	-.01					
.32210000	.01	.57560000	.02	-.20367140	.05	-.10145780	.05	-.20415614	-.01					
.32195000	.01	.67050000	.02	-.20293670	.05	-.10149000	.05	-.20360021	-.01					
.32180000	.01	.76530000	.02	-.20220120	.05	-.10152230	.05	-.20304408	-.01					
.32165000	.01	.85970000	.02	-.20146540	.05	-.10155510	.05	-.20248798	-.01					
.32150000	.01	.95400000	.02	-.20072880	.05	-.10158610	.05	-.20193168	-.01					
.32135000	.01	.10480000	.03	7.19999150	.05	-.10162140	.05	-.20137521	-.01					
.32120000	.01	.11418000	.03	-.19925370	.05	-.10165510	.05	-.20081864	-.01					
.32105000	.01	.12352000	.03	-.19851550	.05	-.10168910	.05	-.20026208	-.01					
.32090000	.01	.13284000	.03	-.19777660	.05	-.10172350	.05	-.19970531	-.01					
.32075000	.01	.14212000	.03	-.19703720	.05	-.10175820	.05	-.19914846	-.01					
.32060000	.01	.15141000	.03	-.19629690	.05	-.10179320	.05	-.19859142	-.01					
.32045000	.01	.16064000	.03	-.19555630	.05	-.10182850	.05	-.19803430	-.01					
.32030000	.01	.16985000	.03	-.19481500	.05	-.10186420	.05	-.19747708	-.01					
.32015000	.01	.17905000	.03	-.19407320	.05	-.10190020	.05	-.19691976	-.01					
.32000000	.01	.18820000	.03	-.19333308	.05	-.10193660	.05	-.19636234	-.01					
R														
.32000000	.01	.18815259	.03	.16791616	.04	.90811522	.03	-.19636334	-.01					
.31200000	.01	.15076874	.03	.16126777	.04	.87176148	.03	-.19230032	-.01					
.30400000	.01	.11319955	.03	.15436806	.04	.83446329	.03	-.18823682	-.01					
.29600000	.01	.75500703	.02	.14719713	.04	.79617044	.03	-.18417343	-.01					
.28800000	.01	.57739259	.02	.13973264	.04	.75682822	.03	-.18011082	-.01					
.28000000	.01	-.19259259	-.02	.13194950	.04	.71637781	.03	-.17604974	-.01					

CASE NO. 11

EE1	.4500000, 07	E2	.1500000, 07	NU1	.3000000, 00	NU2	.9000000, 00	NU3	-.1600000C, 00
-----	--------------	----	--------------	-----	--------------	-----	--------------	-----	----------------

G1 .26785714. 07 G2 .20000000. 06 AA1-.14400000,-02 AA2-.43200000,-01

RI	.32500000	01	RO	.32000000	01	E	.15000000	07	NU	.35000000	00
----	-----------	----	----	-----------	----	---	-----------	----	----	-----------	----

GR-4600000,-02 GTHETA-700C000,-02 GZ-460C000,-02 RG .23000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

81-10451612, 06 82-12750966, 06

AXIAL STRAIN -.43092263,-.02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
32500000	01	40000000	-01	-20261264
32475000	01	15390000	02	-20168118
32450000	01	30700000	02	-20074930
32425000	01	45920000	02	-19981717
32400000	01	61070000	02	-19888467
32375000	01	76150000	02	-19795165
32350000	01	91160000	02	-19701870
32325000	01	10609000	03	-19608521
32300000	01	12097000	03	-19515126
32275000	01	13576000	03	-19421709
32250000	01	15048000	03	-19326258
32225000	01	16513000	03	-19234775
32200000	01	17970000	03	-19141254
32175000	01	19420000	03	-19047700
32150000	01	20863000	03	-18954111
32125000	01	22297000	03	-18860490
32100000	01	23725000	03	-18766823
32075000	01	25145000	03	-18673134
32050000	01	26559000	03	-18579400
32025000	01	27963000	03	-18485640
32000000	01	29359000	03	-18391848
32000000	01	29355118	03	-18391846
31200000	01	23828511	03	-17966442
30400000	01	18140333	03	-17539653
29600000	01	12280492	03	-17111428
28800000	01	62378407	02	-16681714
28000000	01	15555555	-02	-16250451

CASE NO. 12

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.14400000,-02 AA2-.43200000,-01

RI .32800000, 01 RO .32000000, 01 E .15000000, 07 NU .35000000, 00

GR-.46000000,-02 GTHEIA-.70000000,-02 GZ-.46000000,-02 RG .28000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.10451612, 06 B2-.12750966, 06

AXIAL STRAIN --.41373028,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32800000, 01	.60000000,-01	-.19237390, 05	-.90598300, 04	-.19801733,-01
.32760000, 01	.23430000, 02	-.19041530, 05	-.90701300, 04	-.19651517,-01
.32720000, 01	.46610000, 02	-.18845300, 05	-.90806700, 04	-.19501238,-01
.32680000, 01	.69630000, 02	-.18648600, 05	-.90914200, 04	-.19350845,-01
.32640000, 01	.92430000, 02	-.18451540, 05	-.91024200, 04	-.19200388,-01
.32600000, 01	.11508000, 03	-.18254000, 05	-.91136500, 04	-.19049820,-01
.32560000, 01	.13751000, 03	-.18056100, 05	-.91251300, 04	-.18899187,-01
.32520000, 01	.15977000, 03	-.17857740, 05	-.91368300, 04	-.18748453,-01
.32480000, 01	.18183000, 03	-.17658970, 05	-.91487800, 04	-.18597633,-01
.32440000, 01	.20370000, 03	-.17459760, 05	-.91609700, 04	-.18446719,-01
.32400000, 01	.22540000, 03	-.17260110, 05	-.91733900, 04	-.18295712,-01
.32360000, 01	.24688000, 03	-.17060050, 05	-.91860500, 04	-.18144623,-01
.32320000, 01	.26818000, 03	-.16859510, 05	-.91989800, 04	-.17993419,-01
.32280000, 01	.28928000, 03	-.16658550, 05	-.92121300, 04	-.17842131,-01
.32240000, 01	.31017000, 03	-.16457180, 05	-.92255500, 04	-.17690757,-01
.32200000, 01	.33088000, 03	-.16255350, 05	-.92392100, 04	-.17539283,-01
.32160000, 01	.35139000, 03	-.16053060, 05	-.92531200, 04	-.17387710,-01
.32120000, 01	.37170000, 03	-.15850320, 05	-.92672800, 04	-.17236037,-01
.32080000, 01	.39180000, 03	-.15647160, 05	-.92817000, 04	-.17084277,-01
.32040000, 01	.41169000, 03	-.15443550, 05	-.92963700, 04	-.16932422,-01
.32000000, 01	.43137000, 03	-.15239490, 05	-.93113100, 04	-.16780471,-01
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.32000000, 01	.43131174, 03	.35109485, 04	.20738368, 04	-.16780488,-01
.31200000, 01	.35267170, 03	.34857207, 04	.20374831, 04	-.16229734,-01
.30400000, 01	.27054648, 03	.34612796, 04	.20001849, 04	-.15875846,-01
.29600000, 01	.18463029, 03	.34377874, 04	.19618920, 04	-.15418630,-01
.28800000, 01	.94577999, 02	.34154333, 04	.19225498, 04	-.14957878,-01
.28000000, 01	-.11111111,-03	.33944388, 04	.18820994, 04	-.14493351,-01

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILMED.

AFRPL-TR-65-57

APPENDIX E

CALCULATED STRESSES FOR VARIOUS TYPES OF SUBSTRATE GRAPHITE

NOTE: See Appendix F for definitions of symbols used in this Appendix.

AFRPL-TR-65-57

APPENDIX E

PHYSICAL PROPERTIES INPUT DATA

Pyrolytic Graphite:*	Young's Modulus	$E_a = 4.5 \times 10^6 \text{ psi}$
	Young's Modulus	$E_c = 1.5 \times 10^6 \text{ psi}$
	Poisson's Ratio	$\nu_{ac} = 0.90$
	Poisson's Ratio	$\nu_{ca} = 0.30$
	Poisson's Ratio	$\nu_{aa} = -0.16$
	Shear Modulus	$G_a = 0.2 \times 10^6 \text{ psi}$
	Shear Modulus	$G_c = 2.68 \times 10^6 \text{ psi}$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.0049 \text{ in/in}$
	Total Thermal Expansion	$\alpha_c \Delta T = -0.0500 \text{ in/in}$
Molded Substrate (ATJ):**	Young's Modulus	$E = 1.18 \times 10^6 \text{ psi}$
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.00772 \text{ in/in}$
	Total Thermal Expansion	$\alpha_c \Delta T = -0.01029 \text{ in/in}$
High Density Substrate (ZTA):**	Young's Modulus	$E = 2.09 \times 10^6 \text{ psi}$
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion	$\alpha_a \Delta T = -0.00587 \text{ in/in}$
	Total Thermal Expansion	$\alpha_c \Delta T = -0.01827 \text{ in/in}$

APPENDIX E (continued)

Molded Fibrous Substrate (PT-0114):**	Young's Modulus	$E = 0.30 \times 10^6$ psi
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion $\alpha_a \Delta T$	$= -0.00528$ in/in
	Total Thermal Expansion $\alpha_c \Delta T$	$= -0.00714$ in/in
Extruded Substrate (Spear 580):	Young's Modulus	$E = 1.5 \times 10^6$ psi
	Poisson's Ratio	$\nu = 0.35$
	Total Thermal Expansion $\alpha_a \Delta T$	$= -0.0005$ in/in
	Total Thermal Expansion $\alpha_c \Delta T$	$= -0.008$ in/in

-
- * References 7 and 8.
 ** Reference 11.
 *** Reference 10.

CASE NO. 1

F01 .45000000	.07	E2 .15000000	.07	N01 .30000000	.00	N02 .90000000	.00	N03 -.16000000	.00
---------------	-----	--------------	-----	---------------	-----	---------------	-----	----------------	-----

G1 .26785714, C7 G2 .20000000, C6 AA1-.49000000,-02 .AA2-.50000000,-01

	R1	R0	E	NH
00	.56000000	.59000000	.11800000	.35000000

GR-7720000,-02 GTHFA-7720000,-02 GZ-10290000,-01 RG-12900000,01

C11 .63C76036, 07 C12 .21774192, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

91-1466254, 06 32-1616128, 06

AXIAL STRAIN -0.9842451C,-C2

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
560.0000	20.00000	63785000	-22343060	05	-31095008,-02
5615.0000	1070000	14437000	-22263170	05	-31779276,-02
5620.0000	80000000	34664800	-22164880	05	-32462293,-02
5645.0000	7800000	83470000	-22108170	05	-33144061,-02
5660.0000	36300000	13203800	-22073300	05	-33824669,-02
5675.0000	77500000	16035000	-22195940	05	-34504037,-02
5690.0000	13120000	22864000	-21667380	05	-35102235,-02
5705.0000	19720000	27621900	-21616820	05	-35859252,-02
5720.0000	27550000	32378700	-21747760	05	-36535180,-02
5735.0000	36550000	37110500	-21660160	05	-37209518,-02
5750.0000	46750000	41818900	-21614010	05	-37883546,-02
5765.0000	58130000	46502200	-21549300	05	-38556084,-02
5780.0000	70640000	51162700	-21486000	05	-39227511,-02
5795.0000	84310000	55799800	-21424110	05	-39897879,-02
5810.0000	99090000	60413800	-21363550	05	-40567167,-02
5825.0000	11500000	65005100	-21304440	05	-41235455,-02
5840.0000	13197000	69573200	-21246630	05	-41902653,-02
5855.0000	15004000	74119200	-21190160	05	-42568850,-02
5870.0000	16919000	78664300	-21135000	05	-43234058,-02
5885.0000	18937000	83145200	-21081140	05	-43898256,-02
5900.0000	21059000	87625300	-21028560	05	-44561474,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.59000000, 00	-.21063323, 03	.32206456, 03	.56710877, 03	-.44561509, -02
.73000000, 00	-.11826833, 03	.22969967, 03	.56710877, 03	-.55906830, -02
.87000000, 00	-.66778821, 02	.17821015, 03	.56710877, 03	-.67141183, -02
.10000000, 01	-.35173526, 02	.14660485, 03	.56710877, 03	-.78310713, -02
.11500000, 01	-.14391017, 02	.12582234, 03	.56710877, 03	-.89439093, -02
.12900000, 01	.26222221, -03	.11143106, 03	.56710877, 03	-.10053973, -01

CASE NO.	2
E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 -.16000000, 00	
G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01	
R1 .56000000, 00 RC .61000000, 00 F .11800000, 07 NU .35000000, 00	
GR-.77200000,-02 GTHEIA-.77200000,-02 GZ-.10290000,-01 RG .13100000, 01	
C11 .63076036, 07 C12 .21774193, 07 C13 .95046062, 06 C22 .20064516, 07 C44 .20000000, 06	
R1-.14443547, 06 R2-.16166178, 06	
AXIAL STRAIN	-.95580967,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000,-01	.60080400, 04	-.21922700, 05	-.24328408,-02
.56250000, 00	.24020000, 02	.51571100, 04	-.21764230, 05	-.25496496,-02
.56400000, 00	.45660000, 02	.43139200, 04	-.21610570, 05	-.26661555,-02
.56750000, 00	.52620000, 02	.34783900, 04	-.21461600, 05	-.27822433,-02
.57000000, 00	.75790000, 02	.26503200, 04	-.21317270, 05	-.28979641,-02
.57250000, 00	.85240000, 02	.18295700, 04	-.21177450, 05	-.30133270,-02
.57500000, 00	.91060000, 02	.10160600, 04	-.21042050, 05	-.31203346,-02
.57750000, 00	.93310000, 02	.20951000, 03	-.20911000, 05	-.32429987,-02
.58000000, 00	.92000000, 02	-.58989000, 03	-.20784190, 05	-.33575265,-02
.58250000, 00	.67400000, 02	-.13825500, 04	-.20661540, 05	-.34713224,-02
.58500000, 00	.79400000, 02	-.21684600, 04	-.20542950, 05	-.35849922,-02
.58750000, 00	.68260000, 02	-.29478000, 04	-.20428360, 05	-.36983470,-02
.59000000, 00	.52840000, 02	-.37206600, 04	-.20317680, 05	-.38113919,-02
.59250000, 00	.36300000, 02	-.44871200, 04	-.20210830, 05	-.39241297,-02
.59500000, 00	.15690000, 02	-.52473600, 04	-.20107740, 05	-.40365746,-02
.59750000, 00	-.79000000, 01	-.60014100, 04	-.20008330, 05	-.41487244,-02
.60000000, 00	-.34440000, 02	-.67494400, 04	-.19912530, 05	-.42605922,-02
.60250000, 00	-.62850000, 02	-.74915100, 04	-.19820260, 05	-.43721801,-02
.60500000, 00	-.96060000, 02	-.82277300, 04	-.19731460, 05	-.44834949,-02
.60750000, 00	-.13102000, 03	-.89582100, 04	-.19646050, 05	-.45945428,-02
.61000000, 00	-.16869000, 03	-.96830400, 04	-.19563970, 05	-.47053296,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.61000000, 00	-.16872752, 03	.26214945, 03	.89634438, 03	-.47053313,-02
.75000000, 00	-.95803994, 02	.18922590, 03	.89634438, 03	-.58478156,-02
.89000000, 00	-.54494263, 02	.14791617, 03	.89634438, 03	-.69814702,-02
.10300000, 01	-.28851902, 02	.12227381, 03	.89634438, 03	-.81098957,-02
.11700000, 01	-.11850404, 02	.10527231, 03	.89634438, 03	-.92349692,-02
.13100000, 01	-.223308641,-02	.93424240, 02	.89634438, 03	-.10357765,-01

CASE NO.	R	SIGMA R	SIGMA THETA	SIGMA Z	U K
E1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00	.560 0000, 00	.20000000,-01	.13198790, 05	-.21345350, 05	-.15264903,-02
G1 .25785714, 07 G2 .20000000, 06 AA1-.40000000,-02 AA2-.50000000,-01	.564 0000, 00	.86580000, 02	.11777120, 05	-.21038100, 05	-.17194122,-02
RI .56000000, 00 RO .64000000, 00 E .11800000, 07 NU .35000000, 00	.568 0000, 00	.16554000, 02	.10376760, 05	-.20744500, 05	-.19112201,-02
GR-.77200000,-02 GTHETA-.77200000,-02 GZ-.10290000,-01 'RG .13400000, 01	.572 0000, 00	.23250000, 03	.89971200, 04	-.200463850, 05	-.21019530,-02
	.576 0000, 00	.28865000, 03	.76376500, 04	-.20195510, 05	-.22916429,-02
	.580 0000, 00	.33469000, 03	.62976600, 04	-.19539970, 05	-.246803310,-02
	.584 0000, 00	.37100000, 03	.49767100, 04	-.19605940, 05	-.26680417,-02
	.588 0000, 00	.39789000, 03	.36741900, 04	-.194633340, 05	-.26546106,-02
	.592 0000, 00	.41568000, 03	.23896200, 04	-.19241190, 05	-.30406675,-02
	.596 0000, 00	.42467000, 03	.11225000, 04	-.19030960, 05	-.32256394,-02
	.600 0000, 00	.42514000, 03	-.12769000, 03	-.18830520, 05	-.34097563,-02
	.604 0000, 00	.41747000, 03	-.13613700, 04	-.18640120, 05	-.35930503,-02
	.608 0000, 00	.40167000, 03	-.25789500, 04	-.18459440, 05	-.37755302,-02
	.612 0000, 00	.37825000, 03	-.37809200, 04	-.18288200, 05	-.39572531,-02
	.616 0000, 00	.34738000, 03	-.49676900, 04	-.18126100, 05	-.41382200,-02
	.620 0000, 00	.30930000, 03	-.61396300, 04	-.17972860, 05	-.43184589,-02
	.624 0000, 00	.26425000, 03	-.72971400, 04	-.17628200, 05	-.44979966,-02
	.628 0000, 00	.21245000, 03	-.84406000, 04	-.17691870, 05	-.46768557,-02
	.632 0000, 00	.15408000, 03	-.95704100, 04	-.17563630, 05	-.48550606,-02
	.636 0000, 00	.89410000, 02	-.10686840, 03	-.17443210, 05	-.50326275,-02
	.640 0000, 00	.18610000, 02	-.11790260, 05	-.17330380, 05	-.52095804,-02
	R	SIGMA R	SIGMA THETA	SIGMA Z	U K
.640 0000, 00	.18573374, 02	-.29555241, 02	.13128900, 04	-.52095822,-02	
.780 0000, 00	.10710029, 02	-.21692187, 02	.13128899, 04	-.63421615,-02	
.920 0000, 00	.61544137, 01	-.17136571, 02	.13128899, 04	-.74757032,-02	
.106 0000, 01	.32815362, 01	-.14263402, 02	.13128900, 04	-.86098260,-02	
.120 0000, 01	.13540281, 01	-.12335894, 02	.13128900, 04	-.97443267,-02	
.134 0000, 01	-.16898765,-02	-.10980467, 02	.13128899, 04	-.10879086,-01	

CASE NO. 4

E1	.45000000	C7	F2	.15000000	C7	N01	.30000000	C0	N02	.90000000	C0	N03	-.16000000	C0
----	-----------	----	----	-----------	----	-----	-----------	----	-----	-----------	----	-----	------------	----

G1	.26785714,	07	G2	.20000000,	06	A A1-	.49000000,-02	A A2-	.50000000,-01
----	------------	----	----	------------	----	-------	---------------	-------	---------------

RI .1150000, 01 RC .1180000, 01 E .1180000, 07 W' .3500000, 00

GR-7720000,-02 GTHETA-7720000,-02 GZ-10290000,-01 RG-1880000,01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

81-14462547. 06 22-16166128. 06

AXIAL STRAIN. -0.9774106H, -02

R	SIGMA R	SIGMA THETA	SIGMA Z	U K
1150000, 01	0.00000, 00	-0.41866700, 04	-0.21265630, 05	-0.75743725, -02
1151000, 01	-0.56100000, 01	-0.44214600, 04	-0.21231110, 05	-0.76417084, -02
1152000, 01	-0.11510000, 02	-0.46556700, 04	-0.21168950, 05	-0.77089932, -02
1154000, 01	-0.17690000, 02	-0.48892600, 04	-0.21167120, 05	-0.77762191, -02
1156000, 01	-0.24160000, 02	-0.51222900, 04	-0.21135690, 05	-0.78433949, -02
1157000, 01	-0.30930000, 02	-0.53447200, 04	-0.21104570, 05	-0.79105138, -02
1159000, 01	-0.37960000, 02	-0.55865800, 04	-0.21073810, 05	-0.79775817, -02
1160500, 01	-0.45290000, 02	-0.58178400, 04	-0.21043400, 05	-0.80445935, -02
1162000, 01	-0.52880000, 02	-0.60485400, 04	-0.21013320, 05	-0.81115534, -02
1163500, 01	-0.60760000, 02	-0.62786700, 04	-0.20983600, 05	-0.81784634, -01
1165000, 01	-0.68920000, 02	-0.65082200, 04	-0.20954200, 05	-0.82453191, -02
1166500, 01	-0.77340000, 02	-0.67372200, 04	-0.20925150, 05	-0.83121230, -02
1168000, 01	-0.86040000, 02	-0.69656300, 04	-0.20896430, 05	-0.83798750, -02
1169500, 01	-0.95010000, 02	-0.71935000, 04	-0.20868040, 05	-0.84455770, -02
1171000, 01	-1.04260000, 03	-0.74208200, 04	-0.20839990, 05	-0.85122300, -02
1172500, 01	-1.13760000, 03	-0.76475700, 04	-0.20812270, 05	-0.85788300, -02
1174000, 01	-1.23540000, 03	-0.78737800, 04	-0.20784870, 05	-0.86453820, -02
1175500, 01	-1.33560000, 03	-0.80994200, 04	-0.20757190, 05	-0.87116820, -02
1177000, 01	-1.43850000, 03	-0.83245300, 04	-0.20731040, 05	-0.87783340, -02
1178500, 01	-1.54410000, 03	-0.85490900, 04	-0.20704610, 05	-0.88447370, -02
1180000, 01	-1.65230000, 03	-0.877731200, 04	-0.20678500, 05	-0.89110910, -02

R	SIGMA R	SIGMA THETA	SIGMA Z	U K
-11800000, 01	-16523475, 03	38005446, 03	.68393946, 03	-.89110921,-02
-13200000, 01	-11046801, 03	32528771, 03	.68393946, 03	-.10051047,-01
-14600000, 01	-70686427, 02	28550644, 03	.68393955, 03	-.11183516,-01
-16000000, 01	-40683211, 02	25570295, 03	.68393946, 03	-.12310464,-01
-17400000, 01	-17980023, 02	23279976, 03	.68393946, 03	-.13433222,-01
-18800000, 01	-26222221,-03	21481997, 03	.68393946, 03	-.14552728,-01

CASE NO. 5
E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01
R1 .11500000, 01 R0 .12000000, 01 E .11800000, 07 NU .35000000, 00
GR-.77200000,-02 GTHETA-.77200000,-02 G7-.10290000,-01 RG .19000000, 01
C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
R1-.14443527, 06 R2-.16166128, 06

AXIAL STRAIN -.94673764,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.1150000, 01	.10000000,-01	-.13091900, 04	-.20343720, 05	-.68014033,-02	
.11525000, 01	-.32600000, 01	-.17096500, 04	-.20282590, 05	-.69154927,-02	
.11550000, 01	-.73800000, 01	-.21084100, 04	-.20222500, 05	-.70294211,-02	
.11575000, 01	-.12350000, 02	-.25054700, 04	-.20163440, 05	-.71431884,-02	
.11600000, 01	-.18150000, 02	-.29008500, 04	-.20105400, 05	-.72567958,-02	
.11625000, 01	-.24770000, 02	-.32945400, 04	-.20048370, 05	-.73702431,-02	
.11650000, 01	-.32210000, 02	-.36865900, 04	-.19902340, 05	-.74835355,-02	
.11675000, 01	-.40460000, 02	-.40770000, 04	-.19937290, 05	-.75966729,-02	
.11700000, 01	-.49490000, 02	-.44657800, 04	-.19863220, 05	-.77096582,-02	
.11725000, 01	-.59330000, 02	-.48529300, 04	-.19830120, 05	-.78224888,-02	
.11750000, 01	-.69940000, 02	-.52385000, 04	-.19777980, 05	-.79351730,-02	
.11775000, 01	-.81320000, 02	-.56224800, 04	-.19726790, 05	-.80477063,-02	
.11800000, 01	-.93470000, 02	-.60048900, 04	-.19676540, 05	-.81600950,-02	
.11825000, 01	-.10636000, 03	-.63857400, 04	-.19627210, 05	-.82723370,-02	
.11850000, 01	-.12001000, 03	-.67650400, 04	-.19578800, 05	-.83844360,-02	
.11875000, 01	-.13440000, 03	-.71428200, 04	-.19531310, 05	-.84963930,-02	
.11900000, 01	-.14952000, 03	-.75190800, 04	-.19484710, 05	-.86082110,-02	
.11925000, 01	-.16536000, 03	-.78938400, 04	-.19439010, 05	-.87198890,-02	
.11950000, 01	-.18192000, 03	-.82671100, 04	-.19394190, 05	-.88314310,-02	
.11975000, 01	-.19919000, 03	-.86388800, 04	-.19350250, 05	-.89428350,-02	
.12000000, 01	-.21715000, 03	-.90091900, 04	-.19307170, 05	-.90541040,-02	
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.12000000, 01	-.21718569, 03	.50543344, 03	.10715830, 04	-.90541075,-02	
.13400000, 01	-.14563207, 03	.43387981, 03	.10715830, 04	-.10220115,-01	
.14800000, 01	-.93406147, 02	.36165389, 03	.10715830, 04	-.11376319,-01	
.16200000, 01	-.54125491, 02	.34237326, 03	.10715830, 04	-.12525259,-01	
.17600000, 01	-.23840224, 02	.31208799, 03	.10715830, 04	-.13668670,-01	
.19000000, 01	.37876542,-03	.28824739, 03	.10715830, 04	-.14807774,-01	

CASE NO. 6

F1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.40000000,-02 AA2-.50000000,-01

R1 .11500000, 01 R0 .12300000, 01 E .11800000, 07 NU .35000000, 00

GR-.77200000,-02 GTHETA-.77207000,-02 GZ-.10290000,-01 RG .19300000, 01

C11 .63076036, 07 C12 .2174193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.10443347, 06 R2-.16166128, 06

AXIAL STRAIN -.90610993,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.11500000, 01	-.10000000,-01	.2662100, 04	-.19151540, 05	-.57367209,-02	
.11500000, 01	.80900000, 01	.20056600, 04	-.19038570, 05	-.59233024,-02	
.11500000, 01	.13850000, 02	.13497300, 04	-.18928440, 05	-.61094259,-02	
.11620000, 01	.17330000, 02	.69835000, 03	-.16621080, 05	-.62951044,-02	
.11660000, 01	.18550000, 02	.51400000, 02	-.18716480, 05	-.64803418,-02	
.11700000, 01	.17570000, 02	-.59102000, 03	-.18614570, 05	-.66651453,-02	
.11740000, 01	.14410000, 02	-.12291300, 04	-.18515320, 05	-.68495208,-02	
.11760000, 01	.91100000, 01	-.18629400, 04	-.18418680, 05	-.70334793,-02	
.11820000, 01	.17100000, 01	-.24925100, 04	-.18324610, 05	-.72170247,-02	
.11860000, 01	-.77700000, 01	-.31178800, 04	-.18233080, 05	-.74001632,-02	
.11900000, 01	-.19260000, 02	-.37391400, 04	-.16144020, 05	-.75629057,-02	
.11940000, 01	-.32760000, 02	.43563400, 04	-.18057420, 05	-.77652562,-02	
.11980000, 01	-.48220000, 02	-.49695200, 04	-.17973230, 05	-.79472230,-02	
.12020000, 01	-.65620000, 02	-.55787400, 04	-.17691410, 05	-.81288090,-02	
.12060000, 01	-.84910000, 02	-.61840500, 04	-.17611920, 05	-.83100220,-02	
.12100000, 01	-.10607000, 03	-.67855200, 04	-.17734730, 05	-.84908700,-02	
.12140000, 01	-.12906000, 03	-.73831800, 04	-.17659800, 05	-.86713580,-02	
.12180000, 01	-.15385000, 03	-.79770700, 04	-.17587080, 05	-.88517890,-02	
.12220000, 01	-.18042000, 03	-.85673000, 04	-.17516570, 05	-.90312760,-02	
.12260000, 01	-.20875000, 03	-.91538600, 04	-.17448210, 05	-.92107210,-02	
.12300000, 01	-.23879000, 03	-.97368300, 04	-.17361970, 05	-.93898290,-02	
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.12300000, 01	-.23879000, 03	.32664704, 03	.15644291, 04	-.93898293,-02	
.13700000, 01	-.16081100, 03	.48745656, 03	.15644291, 04	-.10580823,-01	
.15100000, 01	-.10349302, 03	.43013857, 03	.15644291, 04	-.11761094,-01	
.16500000, 01	-.60136033, 02	.38678158, 03	.15644291, 04	-.12933373,-01	
.17900000, 01	-.26548513, 02	.35319406, 03	.15644291, 04	-.14099533,-01	
.19300000, 01	-.14859259,-02		.15644291, 04	-.15260907,-01	

CASE NO. 7

F1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

R1 .56000000, 00 K0 .59000000, 00 E .20900000, 07 NU .35000000, 00

GR-.15270000,-01 GTHETA-.18270000,-01 GZ-.58700000,-02 RG .12900000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

H1-.14443547, 06 H2-.16166128, 06

AXIAL STRAIN -.61038639,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.56000000, 00	.20000000,-01	-.44334320, 05	.16761200, 04	-.62277679,-02	
.56150000, 00	-.11898000, 03	-.44756900, 05	.16366300, 04	-.82899804,-02	
.56300000, 00	-.23849000, 03	-.45177970, 05	.15964500, 04	-.83521549,-02	
.56450000, 00	-.35844000, 03	-.45597470, 05	.15556000, 04	-.84143085,-02	
.56600000, 00	-.47890000, 03	-.46015500, 05	.15140800, 04	-.84764460,-02	
.56750000, 00	-.59981000, 03	-.46432040, 05	.14719000, 04	-.85385670,-02	
.56900000, 00	-.72119000, 03	-.46847080, 05	.14200800, 04	-.86006710,-02	
.57050000, 00	-.84209000, 03	-.47260650, 05	.13856200, 04	-.86627580,-02	
.57200000, 00	-.96528000, 03	-.47672820, 05	.13415100, 04	-.87246340,-02	
.57350000, 00	-.10879600, 04	-.48063490, 05	.12968000, 04	-.87868910,-02	
.57500000, 00	-.12111100, 04	-.48492780, 05	.12514600, 04	-.88485370,-02	
.57650000, 00	-.13346500, 04	-.48900630, 05	.12055200, 04	-.89109680,-02	
.57800000, 00	-.14586200, 04	-.49307100, 05	.11589900, 04	-.89729880,-02	
.57950000, 00	-.15830000, 04	-.49712200, 05	.11118600, 04	-.90349970,-02	
.58100000, 00	-.17077800, 04	-.50115920, 05	.10641600, 04	-.90969950,-02	
.58250000, 00	-.18329700, 04	-.50518300, 05	.10158700, 04	-.91589830,-02	
.58400000, 00	-.19585200, 04	-.50919300, 05	.96703000, 03	-.92209590,-02	
.58550000, 00	-.20844500, 04	-.51318970, 05	.91764000, 03	-.92829260,-02	
.58700000, 00	-.22108000, 04	-.51717380, 05	.86767000, 03	-.93448890,-02	
.58850000, 00	-.23374900, 04	-.52114440, 05	.81718000, 03	-.94068400,-02	
.59000000, 00	-.24645400, 04	-.52510210, 05	.76616000, 03	-.94687850,-02	
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.59000000, 00	-.24645579, 04	.37683763, 04	-.32438244, 02	-.94687860,-02	
.73000000, 00	-.13838231, 04	.26876439, 04	-.32438244, 02	-.12225217,-01	
.87000000, 00	-.78135975, 03	.20651805, 04	-.32438244, 02	-.14908340,-01	
.10100000, 01	-.41155516, 03	.17153759, 04	-.32438244, 02	-.17548641,-01	
.11500000, 01	-.16838598, 03	.14722067, 04	-.32438244, 02	-.20161758,-01	
.12900000, 01	.14449382,-02	.13038193, 04	-.32438244, 02	-.22756542,-01	

CASE NO.	R	SIGMA R	SIGMA THETA	SIGMA Z	U	K			
E1	.45000000, 07	E2	.15000000, 07	NU1	.30000000, 00	NU2	.90000000, 00	NU3	-.16000000, 00
G1	.26785714, 07	G2	.20000000, 06	AA1	-.49000000, -02	AA2	-.50000000, -01		
RI	.56000000, 00	RO	.61000000, 00	E	.20900000, 07	NU	.35000000, 00		
GR	-.18270000, -01	GIHFA	-.18270000, -01	GZ	-.58700000, -02	HG	.13100000, 01		
C11	.63076036, 07	C12	.21774193, 07	C13	.95046002, 06	C22	.28064516, 07	C44	.20000000, 06
R1	-.14443547, 06	H2	-.16166128, 06						
AXIAL STRAIN			-.61790623, -02						
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K				
.56000000, 00	.30000000, -01	-.34973350, 05	-.16003000, 03	-.70994272, -02					
.56250000, 00	-.15708000, 03	-.35716580, 05	-.18251000, 03	-.72068007, -02					
.56500000, 00	-.31606000, 03	-.36454800, 05	-.20747000, 03	-.73140551, -02					
.56750000, 00	-.47687000, 03	-.37188070, 05	-.23488000, 03	-.74211935, -02					
.57000000, 00	-.63948000, 03	-.37916520, 05	-.26466000, 03	-.75282220, -02					
.57250000, 00	-.80348500, 03	-.38640220, 05	-.29662000, 03	-.76351454, -02					
.57500000, 00	-.96991000, 03	-.39359230, 05	-.33123000, 03	-.77419658, -02					
.57750000, 00	-.11276500, 04	-.40073650, 05	-.36789000, 03	-.78486693, -02					
.58000000, 00	-.12070200, 04	-.40783540, 05	-.40674000, 03	-.79553187, -02					
.58250000, 00	-.14779600, 04	-.41488990, 05	-.44772000, 03	-.80618582, -02					
.58500000, 00	-.16504400, 04	-.42190010, 05	-.49078000, 03	-.81683086, -02					
.58750000, 00	-.18244300, 04	-.42886770, 05	-.53590000, 03	-.82746780, -02					
.59000000, 00	-.19999000, 04	-.43579280, 05	-.58301000, 03	-.83809700, -02					
.59250000, 00	-.21767900, 04	-.44267600, 05	-.63208000, 03	-.84871830, -02					
.59500000, 00	-.23550800, 04	-.44951850, 05	-.68307000, 03	-.85933260, -02					
.59750000, 00	-.25347300, 04	-.45632010, 05	-.73592000, 03	-.86994000, -02					
.60000000, 00	-.27157200, 04	-.46308220, 05	-.79062000, 03	-.88054090, -02					
.60250000, 00	-.28979900, 04	-.46980490, 05	-.84710000, 03	-.89113540, -02					
.60500000, 00	-.30815300, 04	-.47648930, 05	-.90534000, 03	-.90172430, -02					
.60750000, 00	-.32663100, 04	-.48313550, 05	-.96530000, 03	-.91230730, -02					
.61000000, 00	-.34522800, 04	-.48974440, 05	-.10269300, 04	-.92288520, -02					
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K				
.61000000, 00	-.34523084, 04	.53639122, 04	.23121128, 02	-.92288540, -02					
.75000000, 00	-.19602146, 04	.38718132, 04	.23119321, 02	-.12069798, -01					
.89000000, 00	-.11149719, 04	.30265707, 04	.23119321, 02	-.14808741, -01					
.10300000, 01	-.59029810, 03	.25019018, 04	.23121128, 02	-.17487275, -01					
.11700000, 01	-.24243101, 03	.21540295, 04	.23119321, 02	-.20127086, -01					
.13100000, 01	-.31479012, -02	.19116068, 04	.23121128, 02	-.22740588, -01					

CASE NO. 9

E1 .45000000, 07 E2 .15000000, 07 NU1 .10000000, 00 NU2 .90000000, 00 NU3 .16000000, 00
 G1 .25785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01
 RI .56000000, 00 RO .64000000, 00 E .20900000, 07 NU .35000000, 00
 GR-.1E270000,-01 GTHETA-.1E270000,-01 GZ-.5E700000,-02 KG .13400000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .2E064516, 07 C44 .20000000, 06
 R1-.14443547, 06 R2-.16166128, 06

AXIAL STRAIN --.62244076,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.56000000, 00	.30000000,-01	-.22734750, 05	-.23214500, 04	-.56200011,-02	
.56400000, 00	-.16577000, 03	-.24010980, 05	-.22672700, 04	-.57997441,-02	
.56800000, 00	-.33813000, 03	-.25267010, 05	-.22214300, 04	-.59789092,-02	
.57200000, 00	-.51600000, 03	-.26508210, 05	-.21636500, 04	-.61575752,-02	
.57600000, 00	-.70155000, 03	-.27734780, 05	-.21526400, 04	-.63357643,-02	
.58000000, 00	-.89220000, 03	-.28947790, 05	-.21311700, 04	-.65135023,-02	
.58400000, 00	-.10884600, 04	-.30146910, 05	-.21159500, 04	-.66908024,-02	
.58800000, 00	-.12901900, 04	-.31332600, 05	-.21077500, 04	-.68676925,-02	
.59200000, 00	-.14971000, 04	-.32505760, 05	-.21063500, 04	-.70441865,-02	
.59600000, 00	-.17091500, 04	-.33666100, 05	-.21115000, 04	-.72203026,-02	
.60000000, 00	-.19260400, 04	-.34814230, 05	-.21230000, 04	-.73960636,-02	
.60400000, 00	-.21476100, 04	-.35950410, 05	-.21406300, 04	-.75714027,-02	
.60800000, 00	-.23737000, 04	-.37074730, 05	-.21641800, 04	-.77405767,-02	
.61200000, 00	-.26041400, 04	-.38188100, 05	-.21934700, 04	-.79213638,-02	
.61600000, 00	-.28388000, 04	-.39290230, 05	-.22283200, 04	-.80958609,-02	
.62000000, 00	-.30774900, 04	-.40381550, 05	-.22685300, 04	-.82700799,-02	
.62400000, 00	-.33200900, 04	-.41462360, 05	-.23139400, 04	-.84440380,-02	
.62800000, 00	-.35664500, 04	-.42532890, 05	-.23643800, 04	-.86177490,-02	
.63200000, 00	-.38164500, 04	-.43593360, 05	-.24106900, 04	-.87912320,-02	
.63600000, 00	-.40699100, 04	-.44644150, 05	-.24706900, 04	-.89644880,-02	
.64000000, 00	-.43267700, 04	-.45685340, 05	-.25442700, 04	-.91375410,-02	
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.64000000, 00	-.43267969, 04	.68841549, 04	.15436358, 03	-.91375450,-02	
.78000000, 00	-.24951580, 04	.50525161, 04	.15436358, 03	-.12059213,-01	
.92000000, 00	-.14339890, 04	.39913472, 04	.15436358, 03	-.14854295,-01	
.10600000, 01	-.76475401, 03	.33221127, 04	.15436358, 03	-.17572949,-01	
.12000000, 01	-.31576628, 03	.28731247, 04	.15436358, 03	-.20241925,-01	
.13400000, 01	-.28898765,-02	.25573613, 04	.15436358, 03	-.22876791,-01	

CASE NO. 10

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01

RI .11500000, 01 RO .11800000, 01 E .20900000, 07 NU .35000000, 00

GR-.16270000,-01 GTHETA-.18270000,-01 GZ-.58700000,-02 RG .18800000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.14443547, 06 R2-.16166128, 06

AXIAL STRAIN -.61885563,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.1150000, 01	.00000000, 00	-.50120040, 05	.22207000, 04	-.18352652,-01	
.11515000, 01	-.65410000, 02	-.50317950, 05	.21934900, 04	-.18413281,-01	
.11530000, 01	-.13093000, 03	-.50515540, 05	.21661500, 04	-.18473910,-01	
.11545000, 01	-.19651000, 03	-.50712790, 05	.21386800, 04	-.18534533,-01	
.11560000, 01	-.26219000, 03	-.50909740, 05	.21110800, 04	-.18595157,-01	
.11575000, 01	-.37795000, 03	-.51106360, 05	.20833600, 04	-.18655779,-01	
.11590000, 01	-.39380000, 03	-.51302680, 05	.20555000, 04	-.18716400,-01	
.11605000, 01	-.45972000, 03	-.51498660, 05	.20275300, 04	-.18777018,-01	
.11620000, 01	-.52574000, 03	-.51694320, 05	.199994300, 04	-.18837635,-01	
.11635000, 01	-.59183000, 03	-.51889700, 05	.19712000, 04	-.18898253,-01	
.11650000, 01	-.65801000, 03	-.52084750, 05	.19428500, 04	-.18958869,-01	
.11665000, 01	-.72426000, 03	-.52279490, 05	.19143800, 04	-.19019484,-01	
.11680000, 01	-.79059000, 03	-.52473910, 05	.18857900, 04	-.19080097,-01	
.11695000, 01	-.85700000, 03	-.52668030, 05	.18570800, 04	-.19140711,-01	
.11710000, 01	-.92350000, 03	-.52861850, 05	.18282500, 04	-.19201325,-01	
.11725000, 01	-.99007000, 03	-.53055370, 05	.17993000, 04	-.19261939,-01	
.11740000, 01	-.10567200, 04	-.53248590, 05	.17702200, 04	-.19322553,-01	
.11755000, 01	-.11234400, 04	-.53441480, 05	.17410400, 04	-.19383165,-01	
.11770000, 01	-.11902400, 04	-.53634100, 05	.17117400, 04	-.194443780,-01	
.11785000, 01	-.12571100, 04	-.53826410, 05	.16823200, 04	-.19504393,-01	
.11800000, 01	-.13240600, 04	-.54018410, 05	.16527900, 04	-.19565007,-01	
R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.11800000, 01	-.13240537, 04	.30454427, 04	-.63296501, 02	-.19565011,-01	
.13200000, 01	-.88519529, 03	.26065894, 04	-.63294694, 02	-.22260466,-01	
.14600000, 01	-.56642255, 03	.22878115, 04	-.63296501, 02	-.24922049,-01	
.16000000, 01	-.32760367, 03	.20489926, 04	-.63296501, 02	-.27558652,-01	
.17400000, 01	-.14407536, 03	.18654643, 04	-.63296501, 02	-.30176306,-01	
.18800000, 01	.17545678,-02	.17213923, 04	-.63294694, 02	-.32779242,-01	

CASE NO. 11

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

R1 .11500000, 01 R0 .12000000, 01 E .20900000, 07 NU .35000000, 00

GR-.18270000,-01 GTHETA-.18270000,-01 GZ-.58700000,-02 KG .19000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046062, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.14443547, 06 R2-.16166128, 06

AXIAL STRAIN -.63158212,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	-.10000000,-01	-.43911950, 05	.65471000, 03	-.16830171,-01
.11525000, 01	-.95630000, 02	-.44253700, 05	.62333000, 03	-.16933529,-01
.11550000, 01	-.19158000, 03	-.44594440, 05	.59149000, 03	-.17036859,-01
.11575000, 01	-.28785000, 03	-.44934170, 05	.55921000, 03	-.17140165,-01
.11600000, 01	-.38444000, 03	-.45272910, 05	.52647000, 03	-.17243445,-01
.11625000, 01	-.48133000, 03	-.45610650, 05	.49331000, 03	-.17346700,-01
.11650000, 01	-.57854000, 03	-.45947420, 05	.45970000, 03	-.17449933,-01
.11675000, 01	-.67605000, 03	-.46283320, 05	.42567000, 03	-.17553141,-01
.11700000, 01	-.77386000, 03	-.46618040, 05	.39121000, 03	-.17656330,-01
.11725000, 01	-.87196000, 03	-.46951890, 05	.35634000, 03	-.17759494,-01
.11750000, 01	-.97036000, 03	-.47284800, 05	.32105000, 03	-.17862639,-01
.11775000, 01	-.10690400, 04	-.47616770, 05	.28535000, 03	-.17965765,-01
.11800000, 01	-.11680100, 04	-.47947610, 05	.24924000, 03	-.18068872,-01
.11825000, 01	-.12672700, 04	-.48277920, 05	.21273000, 03	-.18171901,-01
.11850000, 01	-.13667800, 04	-.48607100, 05	.17583000, 03	-.18275031,-01
.11875000, 01	-.14665800, 04	-.48935370, 05	.13854000, 03	-.18378085,-01
.11900000, 01	-.15666500, 04	-.49262720, 05	.10085000, 03	-.18481122,-01
.11925000, 01	-.16669900, 04	-.49589190, 05	.62790000, 02	-.18584146,-01
.11950000, 01	-.17675900, 04	-.49914760, 05	.24340000, 02	-.18687154,-01
.11975000, 01	-.18684400, 04	-.50239440, 05	-.14440000, 02	-.18790147,-01
.12000000, 01	-.19695500, 04	-.50563230, 05	-.53670000, 02	-.18893127,-01

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12000000, 01	-.19695561, 04	.45835118, 04	-.16881678, 02	-.18893129,-01
.13400000, 01	-.13206695, 04	.39346308, 04	-.16879872, 02	-.21658969,-01
.14800000, 01	-.84705852, 03	.34610198, 04	-.16879872, 02	-.24374609,-01
.16200000, 01	-.49084537, 03	.31048012, 04	-.16881678, 02	-.27053064,-01
.17600000, 01	-.21620389, 03	.28301599, 04	-.16881678, 02	-.29703207,-01
.19000000, 01	-.16513580,-02	.26139628, 04	-.16879872, 02	-.32331298,-01

CASE NO. 12

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16~00000, 00
 G1 .26785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01

R1 .11500000, 01 R0 .12300000, 01 E .20900000, 07 NU .35000000, 00

GR-.18270000,-01 GTHEIA-.18270000,-01 GZ-.58700000,-02 RG .19300000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.14443547, 06 R2-.16166128, 06

AXIAL STRAIN --.64257831,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.10000000,-01	-.35740220, 05	-.11475900, 04	-.14815538,-01
.1150000, 01	-.12486000, 03	-.36312880, 05	-.11683400, 04	-.14985957,-01
.1150000, 01	-.25085000, 03	-.36882560, 05	-.11905800, 04	-.15156235,-01
.11620000, 01	-.37792000, 03	-.37449300, 05	-.12142800, 04	-.15326378,-01
.11660000, 01	-.50607000, 03	-.38013130, 05	-.12393900, 04	-.15496391,-01
.11700000, 01	-.63526000, 03	-.38574100, 05	-.12659100, 04	-.15666276,-01
.11740000, 01	-.76547000, 03	-.39132230, 05	-.12938000, 04	-.15836036,-01
.11780000, 01	-.89669000, 03	-.39687570, 05	-.13230500, 04	-.16005678,-01
.11820000, 01	-.10289000, 04	-.40240160, 05	-.13536200, 04	-.16175204,-01
.11860000, 01	-.11620700, 04	-.40790020, 05	-.13855000, 04	-.16344616,-01
.11900000, 01	-.12962000, 04	-.41337200, 05	-.14186600, 04	-.16513921,-01
.11940000, 01	-.14312500, 04	-.41881720, 05	-.14530800, 04	-.16687120,-01
.11980000, 01	-.15672200, 04	-.42423630, 05	-.14687500, 04	-.16852220,-01
.12020000, 01	-.17040900, 04	-.42962950, 05	-.15256300, 04	-.17021222,-01
.12060000, 01	-.18418100, 04	-.43499710, 05	-.15637100, 04	-.17190128,-01
.12100000, 01	-.19804100, 04	-.44033950, 05	-.16029700, 04	-.17358944,-01
.12140000, 01	-.21198500, 04	-.44565710, 05	-.16433800, 04	-.17527673,-01
.12180000, 01	-.22601200, 04	-.45094990, 05	-.16849300, 04	-.17696315,-01
.12220000, 01	-.24011900, 04	-.45621850, 05	-.17276000, 04	-.178664878,-01
.12260000, 01	-.25430700, 04	-.46146320, 05	-.17713800, 04	-.180333365,-01
.12300000, 01	-.26857100, 04	-.46668410, 05	-.18162300, 04	-.18201775,-01
P	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12300000, 01	-.26857341, 04	.63595458, 04	.12424735, 03	-.18201784,-01
.13700000, 01	-.18086276, 04	.54824394, 04	.12424735, 03	-.21049708,-01
.15100000, 01	-.11639694, 04	.48377864, 04	.12424915, 03	-.23829543,-01
.16500000, 01	-.67633555, 03	.43501471, 04	.12424735, 03	-.26558622,-01
.17900000, 01	-.29857657, 03	.39723881, 04	.12424735, 03	-.29248854,-01
.19300000, 01	-.22706172,-02	.36738138, 04	.12424735, 03	-.31908691,-01

CASE NO. 13

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3 .16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

R1 .56000000, 00 R0 .59000000, 00 F .30000000, 06 NU .35000000, 00

GR-.52800000,-02 THETA-.52800000,-02 GZ-.71400000,-02 RG .12900000, 01.

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

H1-.14441547, 00 R2-.16166128, 06

AXIAL STRAIN -.64652565,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.30000000,-01	.68269400, 04	-.81359500, 04	-.20564237,-02
.56150000, 00	.17540000, 02	.62728300, 04	-.80315400, 04	-.21309542,-02
.56300000, 00	.33450000, 02	.57217400, 04	-.79209300, 04	-.22053357,-02
.56450000, 00	.47840000, 02	.51737000, 04	-.78284000, 04	-.22795642,-02
.56600000, 00	.60710000, 02	.46286400, 04	-.77296100, 04	-.23536457,-02
.56750000, 00	.72160000, 02	.40865200, 04	-.76326500, 04	-.24275632,-02
.56900000, 00	.81920000, 02	.35473200, 04	-.75375100, 04	-.25013757,-02
.57050000, 00	.90340000, 02	.30110300, 04	-.74441200, 04	-.25750252,-02
.57200000, 00	.97290000, 02	.24775600, 04	-.73525100, 04	-.26485377,-02
.57350000, 00	.10283000, 03	.19469700, 04	-.72626300, 04	-.27219073,-02
.57500000, 00	.10695000, 03	.14191400, 04	-.71744800, 04	-.27951418,-02
.57650000, 00	.10968000, 03	.89408000, 03	-.70880100, 04	-.28682413,-02
.57800000, 00	.11104000, 03	.37180000, 03	-.70032100, 04	-.29412048,-02
.57950000, 00	.11104000, 03	-.14783000, 03	-.69200800, 04	-.30140403,-02
.58100000, 00	.10970000, 03	-.66476000, 03	-.68365700, 04	-.30867438,-02
.58250000, 00	.10704000, 03	-.11790600, 04	-.67586900, 04	-.31593213,-02
.58400000, 00	.10309000, 03	-.16906000, 04	-.66803800, 04	-.32317668,-02
.58550000, 00	.97830000, 02	-.21997400, 04	-.66036500, 04	-.33040903,-02
.58700000, 00	.91310000, 02	-.27062500, 04	-.65284800, 04	-.33762918,-02
.58850000, 00	.83540000, 02	-.32102000, 04	-.64548500, 04	-.34483693,-02
.59000000, 00	.74530000, 02	-.37116300, 04	-.63827300, 04	-.35203258,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.59000000, 00	.74494377, 02	-.11390397, 03	.18862908, 03	-.35203277,-02
.73000000, 00	.41627825, 02	-.81237422, 02	.18662908, 03	-.42483501,-02
.87000000, 00	.23617625, 02	-.63027214, 02	.18862908, 03	-.49918092,-02
.10100000, 01	.12439825, 02	-.51849422, 02	.18862908, 03	-.57442859,-02
.11500000, 01	.50897185, 01	-.44499303, 02	.18862908, 03	-.65024866,-02
.12900000, 01	-.44444444,-04	-.39409622, 02	.18862906, 03	-.72645478,-02

CASE NO. 14

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01
 R1 .56000000, 00 R0 .61000000, 00 E .30000000, 06 NU .35000000, 00
 GR-.52800000,-02 GTHETA-.52800000,-02 GZ-.71400000,-02 RG .13100000, 01
 C11 .63076036, 07 C12 .2174193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 B1-.14443547, 06 A2-.16166124, 06

AXIAL STRAIN --.61865306,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.56000000, 00	.30000000,-01	.10831140, 05	-.75223900, 04	-.15459059,-02	
.56250000, 00	.46060000, 02	.98855200, 04	-.16723339,-02	-.16723339,-02	
.56500000, 00	.87520000, 02	.89487100, 04	-.71424500, 04	-.17983129,-02	
.56750000, 00	.12450000, 03	.80205400, 04	-.69606600, 04	-.19238519,-02	
.57000000, 00	.15713000, 03	.71008700, 04	-.67641500, 04	-.20489559,-02	
.57250000, 00	.18546000, 03	.61895200, 04	-.66128400, 04	-.21736478,-02	
.57500000, 00	.20959000, 03	.52863500, 04	-.64466100, 04	-.22979218,-02	
.57750000, 00	.22963000, 03	.43912100, 04	-.62853600, 04	-.24217918,-02	
.58000000, 00	.24564000, 03	.35039400, 04	-.61249900, 04	-.25452668,-02	
.58250000, 00	.25774000, 03	.26244600, 04	-.59773800, 04	-.26683518,-02	
.58500000, 00	.26599000, 03	.17525900, 04	-.58304600, 04	-.27910558,-02	
.58750000, 00	.27047000, 03	.88820000, 03	-.56881100, 04	-.29133888,-02	
.59000000, 00	.27127000, 03	.31140000, 02	-.55502800, 04	-.30353577,-02	
.59250000, 00	.26847000, 03	-.81867000, 03	-.54168300, 04	-.31569677,-02	
.59500000, 00	.26212000, 03	-.16614100, 04	-.52877000, 04	-.32782297,-02	
.59750000, 00	.25234000, 03	-.24971300, 04	-.51627900, 04	-.33991467,-02	
.60000000, 00	.23914000, 03	-.33260300, 04	-.50420400, 04	-.35197307,-02	
.60250000, 00	.22265000, 03	-.41481700, 04	-.49253400, 04	-.36399837,-02	
.60500000, 00	.20290000, 03	-.49637000, 04	-.48126300, 04	-.37599167,-02	
.60750000, 00	.17997000, 03	-.57727100, 04	-.47038300, 04	-.38795336,-02	
.61000000, 00	.15393000, 03	-.65753200, 04	-.45988500, 04	-.39988426,-02	
P	SIGMA R	SIGMA THETA	SIGMA Z	U	K
.61000000, 00	.15389312, 03	-.23910698, 03	.25621357, 03	-.39988434,-02	
.75000000, 00	.87380029, 02	-.17259390, 03	.25621357, 03	-.46921291,-02	
.89000000, 00	.49701699, 02	-.13491556, 03	.25621357, 03	-.54170916,-02	
.10300000, 01	.26313451, 02	-.11152739, 03	.25621357, 03	-.61608139,-02	
.11700000, 01	.10806525, 02	-.96020392, 02	.25621357, 03	-.69165619,-02	
.13100000, 01	-.51851851,-04	-.85213814, 02	.25621357, 03	-.76804799,-02	

CASE NO. 15

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01
P1 .54000000, 00 R0 .64000000, 00 F .30000000, 06 NU .35000000, 00
GR-.52800000,-02 GTHETA-.52800000,-02 GZ-.71400000,-02 RG .13400000, 01
C11 .53076036, 07 C12 .21774193, 07 C13 .95046062, 06 C22 .28064516, 07 C44 .20000000, 06
R1-.14443547, 06 R2-.16166128, 06

AXIAL STRAIN --.59149296,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.20000000,-01	.16531770, 05	-.72122600, 04	-.83031950,-03
.56400000, 00	.11172000, 03	.14973480, 05	-.68623900, 04	-.10371407,-02
.56800000, 00	.21096000, 03	.13438800, 05	-.65275300, 04	-.12427170,-02
.57200000, 00	.29816000, 03	.11927070, 05	-.62071700, 04	-.14470872,-02
.57600000, 00	.37374000, 03	.10437620, 05	-.59008400, 04	-.16502895,-02
.58000000, 00	.43806000, 03	.89697600, 04	-.56009000, 04	-.18523647,-02
.58400000, 00	.49154000, 03	.75229500, 04	-.53284700, 04	-.20533430,-02
.58800000, 00	.53450000, 03	.60965400, 04	-.50615700, 04	-.22532652,-02
.59200000, 00	.56733000, 03	.46899800, 04	-.48069900, 04	-.24221605,-02
.59600000, 00	.59034000, 03	.33827500, 04	-.45643200, 04	-.26500617,-02
.60000000, 00	.60384000, 03	.19342600, 04	-.43332100, 04	-.28470029,-02
.60400000, 00	.60816000, 03	.58400000, 03	-.41132800, 04	-.30430162,-02
.60800000, 00	.60363000, 03	-.74843000, 03	-.39041800, 04	-.32381224,-02
.61200000, 00	.59047000, 03	-.20636100, 04	-.37055800, 04	-.34323597,-02
.61600000, 00	.56902000, 03	-.33619700, 04	-.35171600, 04	-.36257529,-02
.62000000, 00	.53951000, 03	-.46439100, 04	-.33385900, 04	-.38183262,-02
.62400000, 00	.50222000, 03	-.59099300, 04	-.31695900, 04	-.40101114,-02
.62800000, 00	.45739000, 03	-.71604000, 04	-.30098700, 04	-.42011297,-02
.63200000, 00	.40524000, 03	-.83957600, 04	-.28591400, 04	-.43914099,-02
.63600000, 00	.34605000, 03	-.96163300, 04	-.27171300, 04	-.45809692,-02
.64000000, 00	.28002000, 03	-.10822510, 05	-.25635600, 04	-.47698354,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.64000000, 00	.28000344, 03	-.44550044, 03	.30959717, 03	-.47698359,-02
.78000000, 00	.16147108, 03	-.32696807, 03	.30959717, 03	-.53971890,-02
.92000000, 00	.92798755, 02	-.25829573, 03	.30959717, 03	-.60816118,-02
.10600000, 01	.49490022, 02	-.21498699, 03	.30959717, 03	-.68004919,-02
.12000000, 01	.20434240, 02	-.16593129, 03	.30959715, 03	-.75417690,-02
.13400000, 01	-.22222222,-04	-.16549702, 03	.30959715, 03	-.82984234,-02

CASE NO. 16

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
G1 .26785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01
RI .11500000, 01 RO .11800000, 01 E .30000000, 06 NU .35000000, 00
GR-.52800000,-02 GTHETA-.52800000,-02 GZ-.71400000,-02 RG .18800000, 01
C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
R1-.14442547, 06 R2-.16166128, 06

AXIAL STRAIN -.63914502,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.1150000, 01	.0000000, 00	.29761800, 04	-.71877200, 04	-.51683169,-02
.11515000, 01	.37100000, 01	.27105200, 04	-.71418700, 04	-.52420156,-02
.11530000, 01	.70600000, 01	.24455300, 04	-.70964600, 04	-.53156513,-02
.11545000, 01	.10060000, 02	.21812600, 04	-.70514800, 04	-.53892120,-02
.11560000, 01	.12700000, 02	.19176700, 04	-.70069200, 04	-.54627087,-02
.11575000, 01	.15000000, 02	.16547700, 04	-.69627900, 04	-.55361345,-02
.11590000, 01	.16950000, 02	.13925500, 04	-.69190900, 04	-.56094942,-02
.11605000, 01	.18560000, 02	.11310400, 04	-.68757900, 04	-.56827839,-02
.11620000, 01	.19830000, 02	.87019000, 03	-.68329200, 04	-.57560086,-02
.11635000, 01	.20750000, 02	.61802000, 03	-.67904500, 04	-.58291683,-02
.11650000, 01	.21350000, 02	.35053000, 03	-.67484000, 04	-.59022590,-02
.11665000, 01	.21600000, 02	.91690000, 02	-.67067600, 04	-.59752867,-02
.11680000, 01	.21530000, 02	-.16647000, 03	-.66655200, 04	-.60482464,-02
.11695000, 01	.21130000, 02	-.42396000, 03	-.66246800, 04	-.61211431,-02
.11710000, 01	.20390000, 02	-.68082000, 03	-.65842500, 04	-.61939768,-02
.11725000, 01	.19330000, 02	-.93700000, 03	-.65442100, 04	-.62667445,-02
.11740000, 01	.17940000, 02	-.11925500, 04	-.65045700, 04	-.63394502,-02
.11755000, 01	.16240000, 02	-.14474300, 04	-.64653300, 04	-.64120899,-02
.11770000, 01	.14210000, 02	-.17016900, 04	-.64264800, 04	-.64846697,-02
.11785000, 01	.11860000, 02	-.19552900, 04	-.63880100, 04	-.65571844,-02
.11800000, 01	.92000000, 01	-.22082600, 04	-.63499300, 04	-.66294401,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11800000, 01	.91954592, 01	-.21149859, 02	.22038090, 03	-.66296393,-02
.13200000, 01	.61477259, 01	-.18102051, 02	.22038092, 03	-.73981031,-02
.14600000, 01	.39338592, 01	-.15888259, 02	.22038090, 03	-.81682055,-02
.16000000, 01	.22752962, 01	-.14229696, 02	.22038090, 03	-.89395165,-02
.17400000, 01	.10007703, 01	-.12955096, 02	.22038092, 03	-.97117443,-02
.18800000, 01	.17037037,-03	-.11954570, 02	.22038090, 03	-.10484683,-01

CASE NO. 17

F1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01
 R1 .11500000, 01 R0 .12000000, 01 E .30000000, 06 NU .35000000, 00
 GR-.52800000,-02 GTHETA-.52800000,-02 GZ-.71400000,-02 RG .19000000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06
 R1-.14441547, 06 R2-.16166128, 06

AXIAL STRAIN --.61061600,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.00000000, 00	.50485800, 04	-.62354900, 04	-.45597706,-02
.11525000, 01	.10480000, 02	.45986800, 04	-.61540700, 04	-.47240742,-02
.11550000, 01	.19920000, 02	.41507400, 04	-.60739100, 04	-.48481798,-02
.11575000, 01	.28350000, 02	.37047900, 04	-.59949600, 04	-.49720873,-02
.11600000, 01	.35800000, 02	.32608000, 04	-.59172200, 04	-.50957969,-02
.11625000, 01	.42260000, 02	.26187700, 04	-.58406800, 04	-.52193105,-02
.11650000, 01	.47740000, 02	.23786500, 04	-.57653200, 04	-.53426340,-02
.11675000, 01	.52270000, 02	.19404400, 04	-.56911400, 04	-.54657600,-02
.11700000, 01	.55630000, 02	.15041200, 04	-.56161200, 04	-.55087112,-02
.11725000, 01	.58460000, 02	.10696800, 04	-.55462500, 04	-.57114667,-02
.11750000, 01	.60140000, 02	.63709000, 03	-.54755200, 04	-.58340393,-02
.11775000, 01	.60920000, 02	.20635000, 03	-.54059100, 04	-.59564289,-02
.11800000, 01	.60770000, 02	-.22256000, 03	-.53374100, 04	-.60786374,-02
.11825000, 01	.59720000, 02	-.64966000, 03	-.52700200, 04	-.62006660,-02
.11850000, 01	.57770000, 02	-.10749600, 04	-.52037200, 04	-.63225186,-02
.11875000, 01	.54940000, 02	-.14984900, 04	-.51365000, 04	-.64441951,-02
.11900000, 01	.51240000, 02	-.19202600, 04	-.50743600, 04	-.65656987,-02
.11925000, 01	.46670000, 02	-.23402700, 04	-.50112700, 04	-.66870310,-02
.11950000, 01	.41230000, 02	-.27585600, 04	-.49492400, 04	-.68061940,-02
.11975000, 01	.34960000, 02	-.31751200, 04	-.48682400, 04	-.69291870,-02
.12000000, 01	.27630000, 02	-.35899700, 04	-.48262700, 04	-.70500130,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12000000, 01	.27817325, 02	-.64737474, 02	.29722994, 03	-.70500160,-02
.13400000, 01	.18652592, 02	-.55572666, 02	.29722997, 03	-.78172543,-02
.14800000, 01	.11963377, 02	-.48883451, 02	.29722997, 03	-.85894322,-02
.16200000, 01	.69321925, 01	-.43852340, 02	.29722994, 03	-.93652689,-02
.17600000, 01	.30531703, 01	-.39973318, 02	.29722994, 03	-.10143891,-01
.19000000, 01	-.35555555,-03	-.36919716, 02	.29722997, 03	-.10924683,-01

CASE NO. 18

F1 .45000000, 07 F2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

R1 .11500000, 01 R0 .12300000, 01 F .30000000, 06 NU .35000000, 00

GR-.52800000,-02 GTHETA-.52800000,-02 GZ-.71400000,-02 RG .19300000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

R1-.14442547, 06 R2-.16166128, 06

AXIAL STRAIN -.58250896,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.60000000, 00	.80421300, 04	-.54532500, 04	-.30027657,-02
.11540000, 01	.26600000, 02	.73081200, 04	-.53118700, 04	-.40045641,-02
.11580000, 01	.50500000, 02	.65794000, 04	-.51737600, 04	-.42058195,-02
.11620000, 01	.71720000, 02	.58558400, 04	-.50388900, 04	-.44065460,-02
.11660000, 01	.90330000, 02	.51374100, 04	-.49071900, 04	-.46067484,-02
.11700000, 01	.10636000, 03	.44240200, 04	-.47786200, 04	-.48061368,-02
.11740000, 01	.11986000, 03	.37156100, 04	-.46531200, 04	-.50056163,-02
.11780000, 01	.13088000, 03	.30121000, 04	-.45306500, 04	-.52043007,-02
.11820000, 01	.13944000, 03	.23134200, 04	-.44111600, 04	-.54024921,-02
.11860000, 01	.14561000, 03	.16195400, 04	-.42742500, 04	-.56002005,-02
.11900000, 01	.14940000, 03	.93033000, 03	-.41809000, 04	-.57974360,-02
.11940000, 01	.15288000, 03	.24577000, 03	-.40700500, 04	-.59942054,-02
.11980000, 01	.15005000, 03	-.43423000, 03	-.39619800, 04	-.61905178,-02
.12020000, 01	.14697000, 03	-.11097100, 04	-.38566700, 04	-.63863763,-02
.12060000, 01	.14170000, 03	-.17807400, 04	-.37540600, 04	-.65817910,-02
.12100000, 01	.13423000, 03	-.24473800, 04	-.36541100, 04	-.67767680,-02
.12140000, 01	.12464000, 03	-.31096900, 04	-.35567800, 04	-.69713140,-02
.12180000, 01	.11294000, 03	-.37677100, 04	-.34620200, 04	-.71654360,-02
.12220000, 01	.99170000, 02	-.44215400, 04	-.33698100, 04	-.73591450,-02
.12260000, 01	.83340000, 02	-.50712100, 04	-.32801000, 04	-.75524460,-02
.12300000, 01	.65540000, 02	-.57167600, 04	-.31928300, 04	-.77453410,-02
.12300000, 01	.65530296, 02	-.15517119, 03	.36285880, 03	-.77453401,-02
.13700000, 01	.44129251, 02	-.13377008, 03	.36285882, 03	-.84949859,-02
.15100000, 01	.28399851, 02	-.11804075, 03	.36285880, 03	-.92562057,-02
.16500000, 01	.16501762, 02	-.10614259, 03	.36285882, 03	-.10026053,-01
.17900000, 01	.72845851, 01	-.96925414, 02	.36285882, 03	-.10802503,-01
.19300000, 01	-.54814814,-03	-.89640355, 02	.36285880, 03	-.11584121,-01

CASE NO. 19

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

RI .56000000, 00 RO .61000000, 00 E .15000000, 07 RU .35000000, 00

GR-.80000000,-02 GTHETA-.50000000,-02 GZ-.50000000,-02 RG .13100000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.14443547, 06 B2-.16166128, 06

AXIAL STRAIN - -.48590031,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.10000000,-01	.20256510, 05	-.30565400, 04	-.28405090,-03
.56250000, 00	.67780000, 02	.19240310, 05	-.28149700, 04	-.41738380,-03
.56500000, 00	.17029000, 03	.18233970, 05	-.25796900, 04	-.55018870,-03
.56750000, 00	.24767000, 03	.17237300, 05	-.23505900, 04	-.68247370,-03
.57000000, 00	.32003000, 03	.16250110, 05	-.21275200, 04	-.81425160,-03
.57250000, 00	.38744000, 03	.15272210, 05	-.19103700, 04	-.94553350,-03
.57500000, 00	.45004000, 03	.14303460, 05	-.16990300, 04	-.10763264,-02
.57750000, 00	.50794000, 03	.13343680, 05	-.14933360, 04	-.12066413,-02
.58000000, 00	.56120000, 03	.12392690, 05	-.12932600, 04	-.13364893,-02
.58250000, 00	.60996000, 03	.11450370, 05	-.10986200, 04	-.14658752,-02
.58500000, 00	.65429000, 03	.10516590, 05	-.90931000, 03	-.15948081,-02
.58750000, 00	.69428000, 03	.95911200, 04	-.72524000, 03	-.17233030,-02
.59000000, 00	.73003000, 03	.86738600, 04	-.54630000, 03	-.18513639,-02
.59250000, 00	.76163000, 03	.77646800, 04	-.37239000, 03	-.19789989,-02
.59500000, 00	.78915000, 03	.68633900, 04	-.20342000, 03	-.21062198,-02
.59750000, 00	.81272000, 03	.59699200, 04	-.39260000, 02	-.22330297,-02
.60000000, 00	.83235000, 03	.50840700, 04	.12015000, 03	-.23594426,-02
.60250000, 00	.84817000, 03	.42057400, 04	.27492000, 03	-.24854625,-02
.60500000, 00	.86024000, 03	.33348000, 04	.42513000, 03	-.26110984,-02
.60750000, 00	.86865000, 03	.24711200, 04	.57089000, 03	-.27363584,-02
.61000000, 00	.87346000, 03	.16145780, 04	.71226000, 03	-.28612483,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.61000000, 00	.87344240, 03	.10836032, 04	.89646129, 03	-.28612510,-02
.75000000, 00	.81319096, 03	.84294333, 02	.52561518, 03	-.39421440,-02
.89000000, 00	.64032807, 03	.62052574, 03	.21842616, 03	-.49965131,-02
.10300000, 01	.43083351, 03	.11602241, 04	-.43791370, 02	-.60397063,-02
.11700000, 01	.21351822, 03	.15964729, 04	-.27259801, 03	-.70791361,-02
.13100000, 01	.29629629,-03	.19625620, 04	-.47540125, 03	-.81186566,-02

CASE NO. 20.

E1	.45000000	.07	E2	.15000000	.07	MU1	.30000000	.00	MU2	.90000000	.00	MU3	-.16000000	.00
----	-----------	-----	----	-----------	-----	-----	-----------	-----	-----	-----------	-----	-----	------------	-----

G1 .26785714. 07 G2 .20000000. 06 AA1-.49000000,-02 AA2-.50000000,-01

RI .56000000. 00	RO .64000000. 00	E .15000000. 07	MU .35000000. 00
------------------	------------------	-----------------	------------------

GR-.80000000,-02 GTMETA-,50000000,-02 GZ-,50000000,-02 RG .13400000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

01-14443547, 06-02-16166120, 06

~~AXIAL STRAIN~~ ~~4700101-02~~

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000	.00	.00000000	.00	.56633400
.56400000	.00	.18704000	.03	.34836360
.56800000	.00	.35976000	.03	.13185910
.57200000	.00	.51845000	.03	.83226400
.57600000	.00	.66416000	.03	.29639090
.58000000	.00	.79673000	.03	.50930440
.58400000	.00	.91682000	.03	.72037980
.58800000	.00	.10248000	.04	.93020430
.59200000	.00	.11210900	.04	.11388108
.59600000	.00	.12060800	.04	.46220000
.60000000	.00	.12801200	.04	.16184000
.60400000	.00	.13435700	.04	.15525227
.60800000	.00	.13967900	.04	.17577002
.61200000	.00	.14400800	.04	.19617987
.61600000	.00	.14737700	.04	.21648572
.62000000	.00	.14981800	.04	.23669067
.62400000	.00	.15135700	.04	.25679751
.62800000	.00	.15202500	.04	.27680956
.63200000	.00	.15184700	.04	.29672931
.63600000	.00	.15085500	.04	.31656036
.64000000	.00	.14906700	.04	.33630431
.64400000	.00	.14906700	.04	.35596465

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.64000000	.00	.14906537	.04	.35596477
.78000000	.00	.11544775	.04	.45652373
.92000000	.00	.83030633	.03	.55718451
.10600000	.01	.52960436	.03	.65833135
.12000000	.01	.25345474	.03	.76115577
.13400000	.01	.21481481	.02	.86258928

CASE NO. 21

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

R1 .56000000, 00 R0 .68000000, 00 E .15000000, 07 NU .35000000, 00

GR-.80000000,-02 GTHETA-.50000000,-02 GZ-.50000000,-02 RG .13800000, 01

C11-.63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.14443547, 06 B2-.16166128, 06

AXIAL STRAIN

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.56000000, 00	.10000000,-01	.35677760, 05	-.48198500, 04	.15999298,-02
.56600000, 00	.36442000, 03	.33085780, 05	-.40771600, 04	.12647522,-02
.57200000, 00	.69432000, 03	.30556330, 05	-.33755300, 04	.93316760,-03
.57800000, 00	.99145000, 03	.28086750, 05	-.27129900, 04	.60502100,-03
.58400000, 00	.12573900, 04	.25674410, 05	-.20876700, 04	.28015540,-03
.59000000, 00	.14936700, 04	.23316840, 05	-.14978100, 04	-.41576200,-04
.59600000, 00	.17017300, 04	.21011810, 05	-.94175000, 03	-.36030580,-03
.60200000, 00	.18829000, 04	.18757030, 05	-.41793000, 03	-.67617240,-03
.60800000, 00	.20385700, 04	.16550510, 05	.75160000, 02	-.98929900,-03
.61400000, 00	.21697100, 04	.14390250, 05	.53890000, 02	-.12998066,-02
.62000000, 00	.22777100, 04	.12274420, 05	.97461000, 03	-.16078083,-02
.62600000, 00	.23635500, 04	.10201230, 05	.13835900, 04	-.19134169,-02
.63200000, 00	.24282700, 04	.81689700, 04	.17669900, 04	-.22167405,-02
.63800000, 00	.24728700, 04	.61761500, 04	.21259900, 04	-.25178711,-02
.64400000, 00	.24982300, 04	.42211500, 04	.24616100, 04	-.28169137,-02
.65000000, 00	.25052500, 04	.23026100, 04	.27749000, 04	-.31139543,-02
.65600000, 00	.24947500, 04	.41908000, 03	.30668100, 04	-.34090869,-02
.66200000, 00	.24675400, 04	-.14306300, 04	.33382800, 04	-.37023895,-02
.66800000, 00	.24243400, 04	-.32478600, 04	.35901500, 04	-.39939491,-02
.67400000, 00	.23658600, 04	-.50337800, 04	.38232700, 04	-.42838447,-02
.68000000, 00	.22928000, 04	-.67894500, 04	.40384200, 04	-.45721433,-02
.68000000, 00	.22927903, 04	-.15340192, 04	.71176588, 03	-.45721450,-02
.82000000, 00	.16155801, 04	-.18168681, 04	.37574514, 03	-.54742282,-02
.96000000, 00	.10940034, 04	-.21036448, 04	.92821481, 02	-.64121816,-02
.11000000, 01	.66944466, 03	-.23771999, 04	-.15151829, 03	-.73762143,-02
.12400000, 01	.31085722, 03	.26329770, 04	.56654599, 03	-.84684819,-02
.13800000, 01	.11111111,-03	-.28706951, 04	-.55854729, 03	-.93611876,-02

CASE NO. 22

E1 .45000000, 07 E2 .15000000, 07 MU1 .30000000, 00 MU2 .90000000, 00 MU3 -.16000000, 00
 G1 .26785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01
 RI .11500000, 01 RO .12000000, 01 E .15000000, 07 NU .35000000, 00
 GR-.80000000,-02 GTHEA-.50000000,-02 GZ-.50000000,-02 RG .19000000, 01
 C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 04
 B1-.14443547, 06 B2-.16166128, 06

AXIAL STRAIN -48969411,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	-.10000000,-01	.10442170, 03	-.16569900, 04	-.30341957,-02
.11525000, 01	.22130000, 02	.99677500, 04	-.15611500, 04	-.31634729,-02
.11550000, 01	.43150000, 02	.94954700, 04	-.14666800, 04	-.32925270,-02
.11575000, 01	.63060000, 02	.90253200, 04	-.13735500, 04	-.34213612,-02
.11600000, 01	.81860000, 02	.85573100, 04	-.12817300, 04	-.35499714,-02
.11625000, 01	.99590000, 02	.80914000, 04	-.11912300, 04	-.36783625,-02
.11650000, 01	.11624000, 03	.76275700, 04	-.11020300, 04	-.38065397,-02
.11675000, 01	.13183000, 03	.71657900, 04	-.10141200, 04	-.39345028,-02
.11700000, 01	.14637000, 03	.67060600, 04	-.92748000, 03	-.40622550,-02
.11725000, 01	.15987000, 03	.62483800, 04	-.84210000, 03	-.41897932,-02
.11750000, 01	.17234000, 03	.57927000, 04	-.75796000, 03	-.43171273,-02
.11775000, 01	.18379000, 03	.53389900, 04	-.67507000, 03	-.44442555,-02
.11800000, 01	.19423000, 03	.48872800, 04	-.59340000, 03	-.45711786,-02
.11825000, 01	.20367000, 03	.44375300, 04	-.51293000, 03	-.46979018,-02
.11850000, 01	.21214000, 03	.39897000, 04	-.43367000, 03	-.48244249,-02
.11875000, 01	.21962000, 03	.35438100, 04	-.35559000, 03	-.49507511,-02
.11900000, 01	.22614000, 03	.30998200, 04	-.27868000, 03	-.50768813,-02
.11925000, 01	.23169000, 03	.26577100, 04	-.20295000, 03	-.52028194,-02
.11950000, 01	.23631000, 03	.22174800, 04	-.12836000, 03	-.53285656,-02
.11975000, 01	.23999000, 03	.17791200, 04	-.54900000, 02	-.54541207,-02
.12000000, 01	.24274000, 03	.13426000, 04	.17420000, 02	-.55794889,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12000000, 01	.24274637, 03	.79137151, 03	.51652939, 03	-.55795000,-02
.13400000, 01	.26802422, 03	.20020588, 03	.31846888, 03	-.67045262,-02
.14800000, 01	.29818977, 03	-.27956151, 03	.14010824, 03	-.78064729,-02
.16200000, 01	.17563948, 03	-.68051936, 03	-.22119611, 02	-.88929910,-02
.17600000, 01	.93442703, 02	.18295674, 04	.17889229, 03	-.99691598,-02
.19000000, 01	.12592592,-02	-.13224592, 04	-.30827196, 03	-.11038447,-01

CASE NO. 23

E1	.45000000	.07	E2	.15000000	.07	N1	.30000000	.00	N2	.90000000	.00	N3	-.16000000	.00
----	-----------	-----	----	-----------	-----	----	-----------	-----	----	-----------	-----	----	------------	-----

G1 .26785714, 07 G2 .20000000, 06 AA1-.49000000,-02 AA2-.50000000,-01

RI .11500000. 01 RO .12300000. 01 E .15000000. 07 NU .35000000. 00

GR-.80000000,-02 GTHETA-,50000000,-02 GZ-,50000000,-02 RG .19300000, 01

C11 .63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.14443547. 06 B2-.16166128. 06

AXIAL STRAIN --- 0.403211769-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000	.20000000	.14137350	-.19564900	-.21021267
.11540000	.47680000	.13365430	-.17900800	-.23115651
.11580000	.92370000	.12599220	-.16272800	-.25203944
.11620000	.13411000	.11838590	-.14680200	-.27286308
.11660000	.17296000	.11083500	-.13122300	-.29362782
.11700000	.20897000	.10333860	-.11598700	-.31433347
.11740000	.24221000	.95896100	-.10108800	-.33498440
.11780000	.27269000	.88506500	-.86521000	-.35557833
.11820000	.30048000	.81169100	-.72281000	-.37611697
.11860000	.32561000	.73883100	-.58362000	-.39660131
.11900000	.34813000	.66648100	-.44758000	-.41703225
.11940000	.36810000	.59463100	-.31466000	-.43741059
.11980000	.38552000	.52327300	-.18480000	-.45773742
.12020000	.40047000	.45240300	-.07595000	-.47801316
.12060000	.41297000	.38201400	.65930000	-.49823870
.12100000	.42508000	.31209800	.18688000	-.51841494
.12140000	.43082000	.24265000	.30498000	-.53854258
.12180000	.43625000	.17366300	.42023000	-.55862231
.12220000	.43939000	.10513200	.53271000	-.57865505
.12260000	.44026000	.37046000	.64242000	-.59864179
.12300000	.43894000	-.30595000	.74946000	-.61858270
.12300000	.43892136	.28698781	.50589181	-.61858313
.13700000	.39642425	-.22331762	.31241092	-.72805544
.15100000	.31885470	-.64471696	.13777181	-.83598997
.16500000	.22154822	-.10021061	.21371629	-.94293850
.17900000	.11346644	.13116672	-.16754866	-.10492668
.19300000	.11851851	-.15843782	-.30270837	-.11552247

CASE NO. 24

E1 .45000000, 07 E2 .15000000, 07 NU1 .30000000, 00 NU2 .90000000, 00 NU3-.16000000, 00

G1 .26785714, 07 G2 .20000000, 06 AAL-.49000000,-02 AA2-.50000000,-01

R1 .11500000, 01 R0 .12700000, 01 E .15000000, 07 NU .35000000, 00

GR-.80000000,-02 GTHEA-.50000000,-02 GZ-.50000000,-02 RG .19700000, 01

C11-.63076036, 07 C12 .21774193, 07 C13 .95046082, 06 C22 .28064516, 07 C44 .20000000, 06

B1-.14443547, 06 B2-.16166128, 06

AXIAL STRAIN-----47564140,-02

R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.11500000, 01	.10000000,-01	.18703410, 05	-.23464100, 04	-.95118200,-03
.11560000, 01	.94020000, 02	.17522200, 05	-.20728000, 04	-.12700749,-02
.11620000, 01	.18099000, 03	.16354230, 05	-.18076600, 04	-.15875178,-02
.11680000, 01	.26109000, 03	.15199220, 05	-.15507600, 04	-.19035487,-02
.11740000, 01	.33452000, 03	.14056900, 05	-.13019100, 04	-.22181986,-02
.11800000, 01	.40141000, 03	.12927010, 05	-.10609100, 04	-.25314955,-02
.11860000, 01	.46195000, 03	.11809260, 05	-.82760000, 03	-.28434754,-02
.11920000, 01	.51627000, 03	.10703410, 05	-.60176000, 03	-.31541683,-02
.11980000, 01	.56455000, 03	.96092200, 04	-.38325000, 03	-.34636002,-02
.12040000, 01	.60693000, 03	.85264600, 04	-.17187000, 03	-.37718021,-02
.12100000, 01	.64353000, 03	.74548600, 04	.32530000, 02	-.40788050,-02
.12160000, 01	.67453000, 03	.63942300, 04	.23013000, 03	-.43846309,-02
.12220000, 01	.70002000, 03	.53443100, 04	.42107000, 03	-.46893148,-02
.12280000, 01	.72017000, 03	.43048900, 04	.60550000, 03	-.49928787,-02
.12340000, 01	.73509000, 03	.32757800, 04	.78359000, 03	-.52953486,-02
.12400000, 01	.74492000, 03	.22567600, 04	.95547000, 03	-.55967495,-02
.12460000, 01	.74977000, 03	.12476400, 04	.11213000, 04	-.58971064,-02
.12520000, 01	.74975000, 03	.24821000, 03	.12811900, 04	-.61964450,-02
.12580000, 01	.74499000, 03	-.74170000, 03	.14353000, 04	-.64947870,-02
.12640000, 01	.73561000, 03	-.17222900, 04	.15837400, 04	-.67921560,-02
.12700000, 01	.72170000, 03	-.26937400, 04	.17266600, 04	-.70885760,-02
R	SIGMA R	SIGMA THETA	SIGMA Z	U R
.12700000, 01	.72167859, 03	-.45978418, 03	.45704207, 03	-.70885782,-02
.14100000, 01	.58401129, 03	-.85838725, 03	.26934744, 03	-.81376391,-02
.15900000, 01	.43801948, 03	-.11978584, 04	.99435407, 02	-.9182.565,-02
.16900000, 01	.29000188, 03	-.14932948, 04	-.55773518, 02	-.10224810,-01
.18500000, 01	.14990040, 03	-.17548141, 04	.19862277, 03	-.11267284,-01
.19700000, 01	.29259259,-02	-.19894755, 04	-.33093640, 03	-.12310725,-01

APPENDIX F

**Nomenclature for Computer
Print-Out Sheets**

APPENDIX F

Nomenclature for Computer Print-Out Sheets

1. Pyrolytic Graphite Properties

E1 - Young's modulus, a-direction, for pyrolytic graphite, psi
 E2 - Young's modulus, c-direction, for pyrolytic graphite, psi
 NU1 - Poisson's ratio, c-a direction, for pyrolytic graphite
 NU2 - Poisson's ratio, a-c direction, for pyrolytic graphite
 NU3 - Poisson's ratio, a-a direction, for pyrolytic graphite
 G1 - Shear modulus in c-direction in pyrolytic graphite, psi
 G2 - Shear modulus in a-direction pyrolytic graphite, psi
 AA1 - Total thermal expansion in a-direction in pyrolytic graphite, inch/inch
 AA2 - Total thermal expansion in c-direction in pyrolytic graphite, inch/inch
 C11
 C12
 C13
 C22
 C44
 B1
 B2

} Derived elastic constants based on property input (Reference 1)

2. Substrate Properties

E - Young's modulus for substrate, psi
 NU - Poisson's ratio for substrate
 GR - Total thermal expansion in radial direction for substrate, inch/inch
 G THETA - Total thermal expansion in hoop direction for substrate, inch/inch
 GZ - Total thermal expansion in axial direction for substrate, inch/inch

3. Dimensions

RI - Radius at free surface of pyrolytic graphite coating, inch
 RO - Radius at coating - substrate interface, inch
 RG - Radius at free surface of substrate, inch

4. Output Data

R - Local radius, inch
 SIGMA R - Radial stress, psi
 SIGMA THETA - Hoop stress, psi
 SIGMA Z - Axial stress, psi
 UR - Radial displacement, inch

PREVIOUS PAGE WAS BLANK, THEREFORE NOT FILMED.

AFRPL-TR-65-57

ADDENDUM

TEST OF THE RESTART CAPABILITY OF A
PYROLYTIC GRAPHITE COATED NOZZLE

INTRODUCTION

During the program described in the main body of this report, five subscale and four fullscale pyrolytic graphite coated nozzles were motor tested with an advanced high performance propellant. These firing tests demonstrated that nozzles of useful size coated with pyrolytic graphite can provide good performance under severe service conditions. Although feasibility was clearly demonstrated for pyrolytic graphite coated nozzles, further work remains to be carried out in several areas to fully exploit the capabilities of this unique, lightweight nozzle design. Optimization of the coating-substrate composite for maximum erosion resistance is needed. One of the facets of particular interest is an investigation of the restart capability of pyrolytic graphite coatings.

Restart capability is of such current interest that Atlantic Research Corporation requested the permission of the Air Force to include an additional firing test in the current program in which a subscale nozzle would be re-fired in a second test. Permission was granted for this restart test and this addendum documents the successful completion of this additional task.

CONFIDENTIAL

AFRPL-TR-65-57

RESULTS

The pyrolytic graphite coated insert selected for the restart test was the insert first tested in firing KPb-6. In this first test an erosion rate of 0.64 mil/sec was measured for a firing duration of 37.3 seconds at an average motor pressure of 530 psi. The insert appeared to be in good shape following the first test and microscopic examination revealed no delamination flaws before or after firing KPb-6. The coating on this insert was the first prepared on the fibrous graphite type of substrate. Careful macroscopic examination of the surface of the once-tested coating indicated areas of surface roughness related no doubt to the fact that the coating quality had not been optimized for this system. A close-up photograph of the coated insert after firing KPb-6 and prior to the restart test (firing KPb-10) is shown in Figure 34. Nevertheless, it was concluded that this insert was suitable for studying the restart behavior of a pyrolytic graphite coating. (C)

The once-tested insert was assembled into the standard subscale nozzle unit (see Figure 15). The ATJ graphite and edge-oriented pyrolytic graphite entrance pieces were also re-used from firing KPb-6. Thus, the entire nozzle contour from an upstream area ratio of about six through the throat region was made up of components which were undergoing restart operation. Several of the back-up and insulation components were replaced only because of mechanical damage during disassembly after firing KPb-6 and before plans were made for the restart test. Overall, then, the restart test was a good test of all the critical components of a pyrolytic graphite coated nozzle. (U)

The restart test was firing KPb-10 and consisted of a 15.1-second duration test at an average motor pressure of 532 psia with 6550°F propellant (APC-112). The firing was a complete success with an average erosion rate based on before and after test measurements of the throat diameter of 0.53 mil/sec. The throat was somewhat oval after the first firing with a difference in the maximum and minimum diameters of some 20 mil. After the second firing the ovalness was still the same which indicates no further selective erosion. The motor pressure-time trace for the restart firing KPb-10 is shown in Figure 35. A close-up oblique view of the nozzle throat region looking from the entrance end is shown in Figure 36. (C)

Microscopic examination of the polished cross section of the coating after its second test revealed no change in structure and no delamination flaws. Thus, no degradation of the coating quality was visible after either one or two firing cycles. The remaining coating thickness at the edge of the coated section, where it was thinnest initially, appears insufficient to allow further testing, but the cumulative firing time on this insert is already 52.4 seconds. (U)

The erosion rate observed in the second firing was somewhat lower than in the first test. However, if an induction period of only about two seconds prior to the onset of erosion were assumed, the erosion data would be comparable. It is indicated, therefore, that the rapid heating of the coating surface predicted by thermal analysis is consistent with the experimental data. (U)

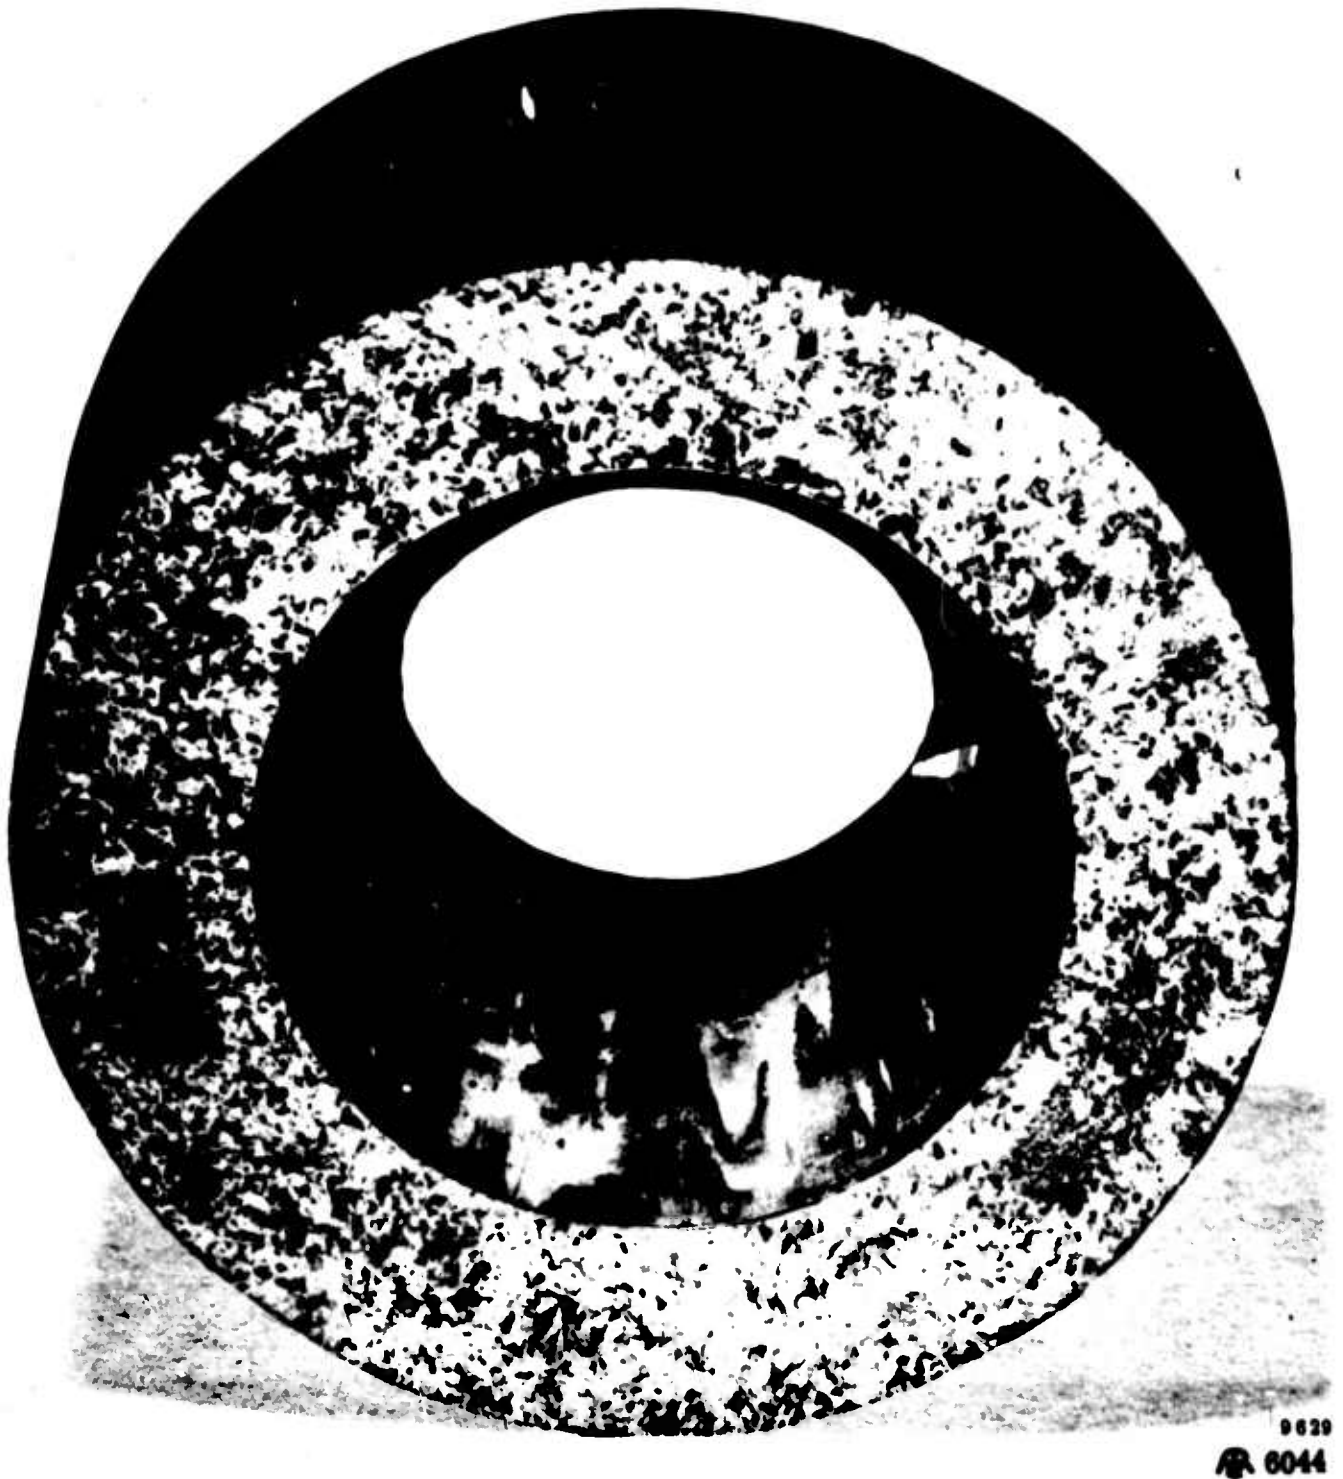


Figure 34. Macro-View (3X) of Coated Insert Prior to Restart Test.

CONFIDENTIAL

6107

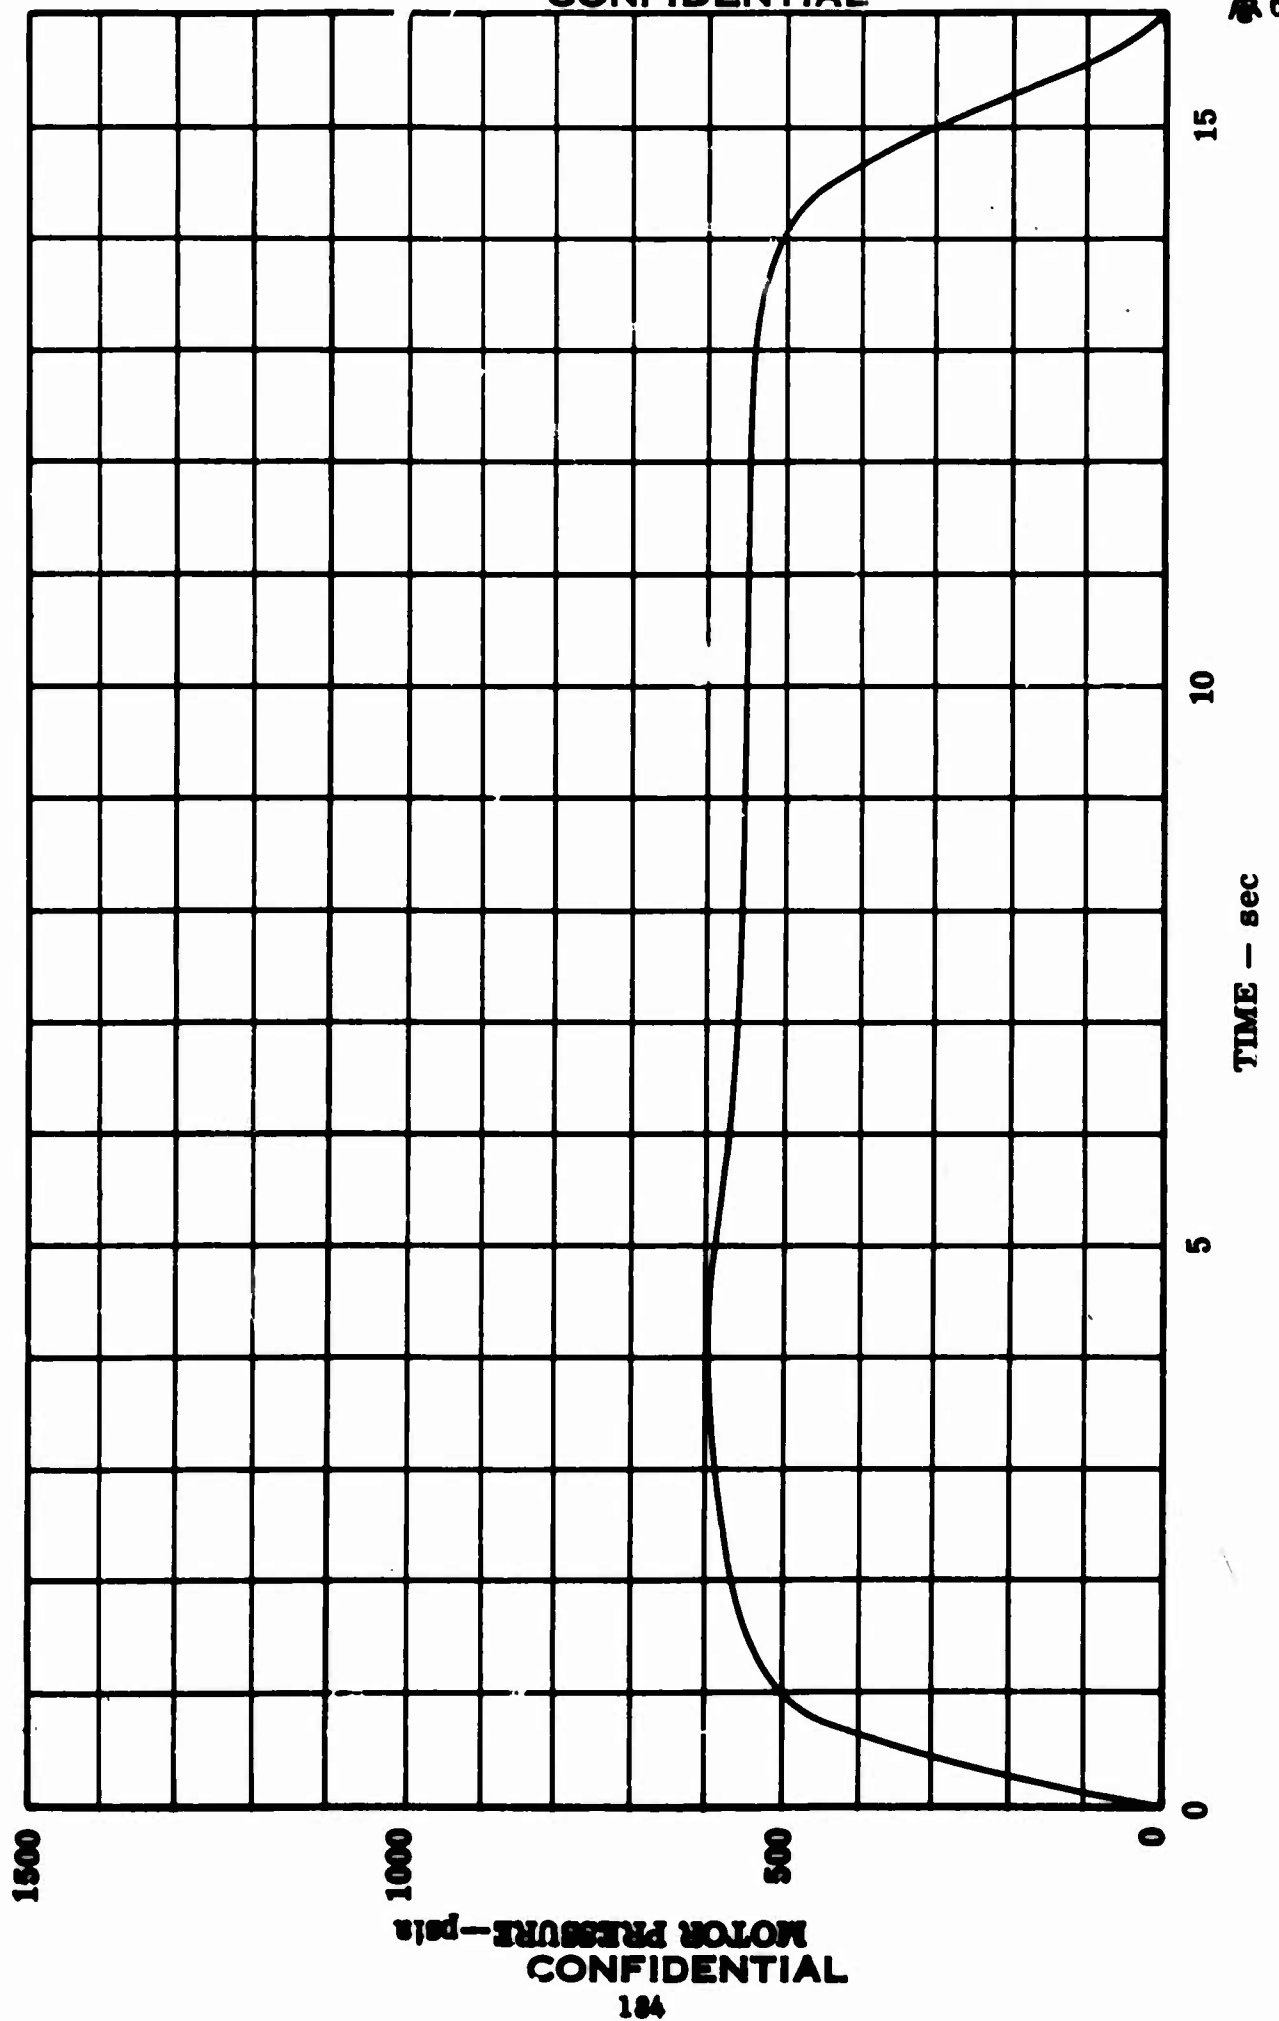


Figure 35. Motor Pressure Trace for Firing Sub-scale Number 6.

CONFIDENTIAL



9636

AR 6043

**Figure 36. Close-Up Oblique View of Nozzle (from Entrance)
after Restart Test.**

CONCLUSIONS

The results of the work described in the main body of this report demonstrated that pyrolytic graphite coatings which are free of delamination flaws can provide good nozzle performance. A second firing test of one coated insert described in this addendum demonstrated that such a nozzle can withstand restart service conditions. The complete criteria for suitable restart performance and the duty cycle limitations could not be defined by a single test, but the successful performance of the insert in two firings proves that pyrolytic graphite coated nozzles are good candidates for restart operation.

UNCLASSIFIED

Security Classification

DOCUMENT CONTROL DATA - R&D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author) Atlantic Research Corporation Alexandria, Virginia		2a. REPORT SECURITY CLASSIFICATION CONFIDENTIAL	
		2b. GROUP 4	
3. REPORT TITLE FEASIBILITY DEMONSTRATION OF PYROLYTIC GRAPHITE COATED NOZZLES			
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Final Report, February 1964 to March 1965			
5. AUTHOR(S) (Last name, first name, initial) Batchelor, James D. Ford, Edwin F. Olcott, Eugene L.			
6. REPORT DATE March 1965		7a. TOTAL NO. OF PAGES 186	7b. NO. OF REFS 11
8a. CONTRACT OR GRANT NO. AF 04(611)-9708 a. PROJECT NO. 3059 c. Task No. 03 d.		8b. ORIGINATOR'S REPORT NUMBER(S) TR-PL-6839-01-0 8c. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
10. AVAILABILITY/LIMITATION NOTICES Qualified requesters may obtain copies from DOC.			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY Rocket Propulsion Laboratory Edwards, California	
13. ABSTRACT Pyrolytic graphite coatings have been found to be highly erosion resistant under severe rocket nozzle conditions. The objective of this program was to demonstrate the feasibility of such coatings for nozzles up to 2.3-inch diameter in firings at 700 psi with a 6550°F propellant. This objective was accomplished. Stress analyses and thermal analyses were carried out in support of the design, fabrication, and motor testing of nozzles of both 1.1-inch and 2.3-inch diameter. Thermal analysis indicated the potential of pyrolytic graphite coatings for lightweight nozzle designs. The results of the stress analyses for coated composites were correlated with experimental evidence of delamination cracking in the coatings. Critical stress levels were identified for both radial tension in the coating and axial tension in the substrate. The deposition process was improved to produce crack-free coatings 50-mil-thick on conventional graphite substrates and 100-mil thick on a fibrous graphite substrate. Nine motor firing tests were made and good performance was demonstrated with both subscale and full-scale nozzles. The presence of microscopically observed delamination cracks was found to destroy the integrity of pyrolytic graphite coatings during nozzle service. For coatings without major cracks coating integrity was achieved, however, and erosion rates of acceptable magnitude were measured for subscale nozzles for durations up to about 40 seconds. In full-scale nozzles satisfactory erosion rates were measured for firings of durations up to 60 seconds. Optimization of the coating to provide minimum erosion rates should result in still further performance improvements.			

DD FORM 1 JAN 64 1473

Security Classification

UNCLASSIFIED
Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Rocket nozzles materials pyrolytic graphite						

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (corporate author) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parentheses immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____"
- (4) "U. S. military agencies may obtain this report directly from DDC. Other qualified agencies shall request through _____"
- (5) "All distribution of this report is controlled. DDC users shall request through _____"

If the report has been furnished to the U. S. Services, Department of Commerce, for sale, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for supplementary notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the departmental project office or laboratory (or) the research and development.

13. **ABSTRACT:** Enter an abstract giving summary of the document indicative of its content. It may also appear elsewhere in the report. If additional space is required, it may be attached.

It is highly desirable that the abstract be unclassified. Each paragraph of the abstract should contain an indication of the military security classification in the paragraph, represented by a letter.

There is no limitation on the length of the abstract, however, the suggested length is from 1 to 200 words.

14. **KEY WORDS:** Key words are terms or short phrases that characterize the report and are used as index entries for cataloging the report. They are selected so that no security classification is required, such as equipment model designations, project code name, geographic location, etc. The assignment of links, if any, is indicated by the letter in parentheses following the key word.