

UNCLASSIFIED

AD NUMBER
AD401004
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution authorized to U.S. Gov't. agencies and their contractors; Foreign Government Information; APR 1962. Other requests shall be referred to US Library of Congress, Attn: Aerospace Technology Directorate, Washington, DC.
AUTHORITY
ATD ltr 2 Dec 1965

THIS PAGE IS UNCLASSIFIED

401004

S/817/62/005/000/002/012
A006/A101

ASTIA FILE COPY

STEP
 AUTHORS: (c) Polyvyanhyy, I. R., Avrov, V. G.
 TITLE: (b) Investigating kinetics of thermochemical dissociation of sodium sulfate in the presence of vanadium pentoxide
 SOURCE: (S) Akademiya nauk Kazakhskoy SSR. Institut metallurgii i obogashcheniya. Trudy. v. 5, 1962, Tsvetnaya metallurgiya. 41 - 48

TEXT: The investigation was made for the purpose of revealing the basic kinetic regularities in the thermochemical dissociation, depending on temperature, sintering duration and the amount of vanadium pentoxide. The sodium sulfate and vanadium pentoxide mixture was placed in a preheated tubular electric furnace to determine the SO₃ amount which, after Na₂SO₄ dissociation, is supplied to an absorption column. Qualitative experiments were performed to estimate the dissociation rate; the batch was placed into a cold furnace which was then heated to the required temperature (20 to 1,250°C). The experiments show that the beginning of the thermochemical dissociation of Na₂SO₄ in the presence of V₂O₅ depends upon the amount of V₂O₅. Pure sodium sulfate begins to dis-


Card 1/3

ciate at 900°C; if V₂O₅ is added in a ratio of 10 : 1, dissociation begins at 600°C; at a stoichiometric ratio $\frac{Na_2SO_4}{V_2O_5} = \frac{1}{1}$, the temperature of visible disso-

ciation drops to 500°C. The rate and degree of dissociation increase sharply with higher temperatures and extended sintering time, namely from 2.84% at 600°C and 60 minutes sintering time (at a 1 : 1 molar ratio of the substances) to 93.5% at 1,000°C. Variations in the dissociation with time are graphically expressed by parabolic curves. A decrease in the V₂O₅ amount in the mixture reduces the rate and degree of sodium sulfate dissociation from 93.5 to 16.85% at a 1 : 1 and 10 : 1 ratio, respectively, and 60 minutes sintering time. An analysis of the results of phase transformations leads to the conclusion that a higher dissociation rate of Na₂SO₄ in the presence of V₂O₅, in particular at 850°C and more, is due to the formation of sodium vanadate from the dissociation product of sodium sulfate and vanadium pentoxide; the formation of a liquid phase, promoting the rate of mass transfer, and to the catalytic effect of V₂O₅ on the reaction of sodium sulfate dissociation. The process is described by the

Card 2/3

following summary reactions:

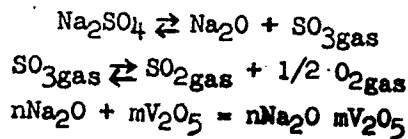

There are 4 figures and 1 table.