

**UNCLASSIFIED**

**AD** 404 860

**DEFENSE DOCUMENTATION CENTER**

**FOR**

**SCIENTIFIC AND TECHNICAL INFORMATION**

**CAMERON STATION, ALEXANDRIA, VIRGINIA**



**UNCLASSIFIED**

**NOTICE:** When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

404 860

BUREAU OF SHIPS TRANSLATION NO. 817

THIS DOCUMENT MAY BE RELEASED WITH NO RESTRICTIONS ON DISSEMINATION

ORGANOSILICON COMPOUNDS CONTAINING PHOSPHORUS  
(Kremiyorganicheskiye soedineniya, soderzhashohiye fosfor)

by

M. A. Galashina, M. V. Sobolevskii, K. A. Andrianov,  
T. P. Alekseyeva

CATALOGUED BY ASTIA  
AD No. 404860

Translated from

Plasticheskiye  
massy  
No. 4, 1962.  
pp. 16 - 19

by

Scripta Technica, Inc.  
1000 Vermont Avenue, N.W.  
Washington, D.C.

DDC  
RECEIVED  
MAY 29 1963  
TISA A



May 1963

BUREAU OF SHIPS · NAVY DEPARTMENT · WASHINGTON 25, D.C.



Trifunctional alkylalkoxysilanes react with  $P_2O_5$  as follows:




The corresponding polymers, which are solids, are separated.

The reaction of chloromethyldimethylethoxysilane or dichloromethyldimethylethoxysilane with phosphorus pentoxide at 200 - 210° gives rise<sup>5</sup> to polymers corresponding to the structures:



and




By refluxing for two hours 0.1 mole of hexaalkyldisiloxane and 0.5 mole of phosphorus pentoxide, tris(trialkylsilyl) phosphates, which are viscous, colorless, sufficiently heat-stable liquids (when  $R = CH_3$  and  $C_2H_5$ ) are obtained in 80% yield<sup>6</sup>.


If hexaalkyldisiloxane and phosphorus pentoxide are taken in equimolar quantities, tris(trialkylsilyl) phosphate<sup>7</sup> is obtained:



If, however, excess phosphorus pentoxide is added, a solid polymer, trialkylsilylpyrophosphate, is chiefly obtained:




On heating with hexaalkyldisiloxane, this metastable compound can be converted into tris(trialkylsilyl) phosphate:




It has also been found possible to obtain tris(trialkylsilyl) phosphates by the reaction of trialkylalkoxy - or trialkylchlorosilane with phosphoric acid, and also with trialkyl phosphate<sup>8</sup>.

Chlorides of silicophosphoric acids, containing the  $\begin{array}{c} \vdots \\ -Si-O-P= \\ \vdots \quad \parallel \end{array}$  bond, which can be used to prepare organosilicon polymers with phosphorus in the end groups, have also been described<sup>9, 10</sup>. These compounds have proven unstable to hydrolysis<sup>11</sup>. In all cases, the hydrolysis takes place primarily at the  $\begin{array}{c} \vdots \\ -Si-O-P= \\ | \quad \parallel \end{array}$  bond, irrespective of whether monomeric silicophosphates or polymers are subjected to hydrolysis:




The stability to hydrolysis increases somewhat if the organic radical of the silicon atom is replaced by a trialkylsilyl group. But even these compounds can hydrolyze in several minutes<sup>12</sup>.

By reacting trialkylchlorosilane with sodium dialkyl phosphate,



several silicon phosphororganic compounds have been obtained<sup>7, 13</sup> which contain the



A study was made of the reaction of sodium or potassium hydrophosphide with trialkylfluorosilane with the aim of investigating the heteroorganic compounds in which silicon is linked directly to phosphorus<sup>14</sup>:




The structure of the substances obtained is confirmed by the formation of phosphine and hexamethyldisiloxane in hydrolysis with water or an aqueous solution of alkali, as in the equation:



As shown by the works cited above, the  $\begin{array}{c} | \\ -\text{Si}-\text{P}- \\ | \quad | \end{array}$  bond is still less stable to hydrolysis than the  $\begin{array}{c} | \\ -\text{Si}-\text{O}-\text{P}=\text{bond.} \\ | \quad || \end{array}$

Thus, the alcoholysis of bis(*n*-butyl)trimethylsilyl phosphate occurs readily in the presence of alcohol or even phenol. This compound reacts rather easily with aniline and *n*-butylamine, and also with *n*-butyl mercaptan<sup>13</sup>.

As we know, esters of thiophosphoric acid are much more stable to hydrolysis than those of phosphoric acid<sup>15</sup>. In order to examine the effect of the introduction of sulfur on the stability to hydrolysis of compounds containing the  $\begin{array}{c} | \\ -\text{Si}-\text{O}-\text{P}=\text{bond,} \\ | \quad || \end{array}$  condensed sulfur-containing products with the structural units




were synthesized and their properties investigated<sup>16</sup>.

All the prepared esters of silicothiophosphoric acid hydrolyze easily. Neither the introduction of a second sulfur atom nor the creation of the  $\begin{array}{c} | \\ -\text{Si}-\text{S}-\text{P}-\text{bond} \\ | \quad || \end{array}$  has shown any positive effect on the stability to hydrolysis.

A description<sup>17</sup> has been given of the synthesis of organosilicon esters of dithiophosphoric acid, which were obtained by the reaction of vinylalkylsilanes and allylalkylsilanes with dialkyldithiophosphoric acids.



The copolymerization of 1,3-diene hexaorganosiloxanes having the general formula

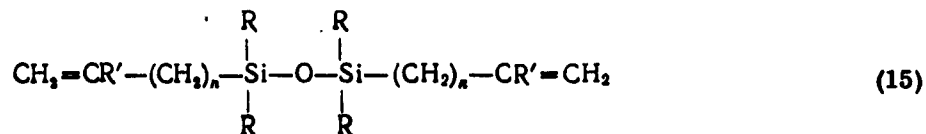


with alkylphosphines in the presence of catalysts or ultraviolet light produces polymers containing phosphorus in the principal chain<sup>24</sup>.

To prepare heat-stable polymers, attempts have been made to carry out the condensation of phosphonitrile chloride trimer with diphenyldihydroxysilane as in the synthesis of organic esters. However, no reactions took place even on heating between 180 and 220° for 3 to 5 hours: neither chlorine, nor water, nor hydrogen chloride was evolved<sup>25</sup>.

Compounds containing boron and phosphorus in the chain, the dimethylphosphineborine cyclic polymers have been described<sup>26</sup> as being stable at temperatures above 500°.

The object of this work was the preparation of silicon phosphororganic monomers and polymers containing the grouping  $-\underset{\text{S}}{\overset{\text{S}}{\text{Si}}}-\text{C}-\text{O}-\text{P}-$ , and their condensation with  $\alpha, \omega$ -dichloropolydimethylsiloxanes.


The diethylthiophosphatomethyldimethylethoxysilane monomer was obtained by the reaction of chloromethyldimethylethoxysilane and sodium diethylthiophosphate according to the equation:



This reaction takes place readily in an alcohol medium with an appreciable yield of diethylthiophosphatomethyldimethylethoxysilane. The synthesized diethylthiophosphatomethyldimethylethoxysilane is a liquid which distills under vacuum without decomposing.

The condensation of diethylthiophosphatomethyldimethylethoxysilane with

$\alpha$ ,  $\omega$ -dichloropolydimethylsiloxanes takes place as follows:

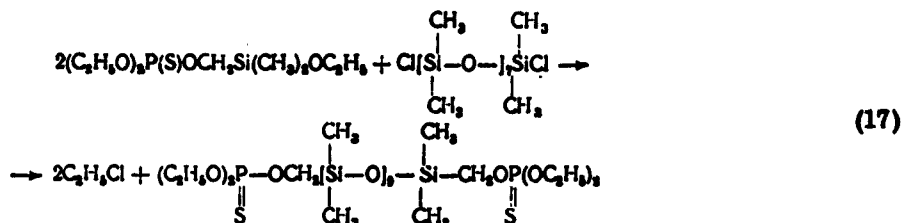

This reaction was also carried out for other  $\alpha$ ,  $\omega$ -dichloropolydimethylsiloxanes with the degree of polymerization  $\omega=4, 5, 6$  and  $7$ .

Analysis for the carbon, phosphorus and silicon content of the products obtained was performed on a single sample, using a method due to B. M. Luskin<sup>27, 28</sup> (method of wet combustion).

## EXPERIMENTAL

### 1. Preparation of Diethylthiophosphatomethylidimethylethoxysilane

To a four-necked flask provided with a mechanical stirrer, a reflux condenser, a dropping funnel and a thermometer is added 24.6 g of diethylchlorothiophosphate and, on cooling (at  $0^\circ$ ), an alcohol solution of an equimolar amount of sodium hydroxide is added dropwise. The mixture is brought to room temperature and stirred for half an hour. Two to three drops of pyridine are then added with 20.1 g of chloromethylidimethylethoxysilane, which is added dropwise, and the mixture is refluxed for three hours.

The precipitate of sodium chloride formed is filtered out, the alcohol is distilled from the filtrate, the residue is dried over calcium chloride and distilled under reduced pressure.

The yield of diethylthiophosphatomethylidimethylethoxysilane, a transparent, colorless liquid, was 19.5 g (52% of theoretical). B. P.,  $89-94^\circ$  (at 15 mm),  $d_4^{20}$ , 1.0581;  $n_D^{20}$ , 1.4450; molecular refraction: calculated, 71.60; found, 71.93.

For  $\text{C}_9\text{H}_{23}\text{O}_4\text{SiPS}$ , we found, %: C-37.4; 37.8; Si-9.26; 9.05; P-10.7; 10.6.  
Calculated, %: C-37.7; Si-9.8; P-10.8.

## 2. Condensation of Diethylthiophosphatomethyldimethylethoxysilane with $\alpha, \omega$ -Dichloropolydimethylsiloxanes

A mixture of  $\alpha, \omega$ -dichloropolydimethylsiloxane ( $\omega = 4, 5, 6, 7, 8$ ) and diethylthiophosphatomethyldimethylethoxysilane, taken in the ratio of 1:2, is heated for three hours in the presence of 0.5%  $\text{FeCl}_3$ , at an elevated temperature in a four-necked

flask provided with a mechanical stirrer, a thermometer and an outlet for the ethyl chloride being formed. After the reaction mixture has cooled, it is distilled under vacuum. The  $\alpha, \omega$ -bis(diethylthiophosphatomethyl) polydimethylsiloxanes boil in

the 130–165° range (at 1.5 mm).

For  $\begin{matrix} \text{C} & \text{H} & \text{O} & \text{Si} & \text{P} & \text{S} \\ 30 & 84 & 18 & 10 & 2 & 2 \end{matrix}$  we calculated, %: C—33.0; Si—25.73; P—5.67.

Found, %: C—33.4; 33.16; Si—26.14; 26.20; P—4.68; 4.59.

### CONCLUSIONS

1. A new monomer, diethylthiophosphatomethyldimethylethoxysilane, was obtained.

2. The reaction of condensation of diethylthiophosphatomethyldimethylethoxysilane with  $\alpha, \omega$ -bis(dichloro) polydimethylsiloxanes was studied, and the possibility of synthesizing an oligomer of  $\alpha, \omega$ -bis(diethylthiophosphatomethyl) polydimethylsiloxanes was demonstrated.

### REFERENCES

1. Alfrey, F., Tohn, F., Mark, H., *Polimer, J.*, **1**, 102 (1946).
2. Brit. pat. 687759 (1953); *Referativniy zhurnal, Khimiya*, **11**, 405, 22524 P (1955).
3. Kreshkov, A. P., Karateyev, D. A., *Zhurnal prikladnoi khimii* No. 9, 1416 (1957).
4. Kreshkov, A. P., Karateyev, D. A., *Zhurnal organicheskoi khimii* **29**, No. 12, 4082 (1959).
5. Kreshkov, A. P., Karateyev, D. A., *Avt. Svid.* 127262 (1960); *Byull. izobr.* No. 7, 17 (1960).
6. Voronkov, M. G., *Zhurnal organicheskoi khimii* **25**, 469 (1955).
7. Feher, F., Kuhlorsch, G., *Chem. Ber.*, No. 1, 134 (1957).
8. Voronkov, M. G., Zgonnik, V. N., *Zhurnal organicheskoi khimii* **27**, 1483 (1957).
9. Fertig, J., Gerrard, W., *Chem. a. Ind.*, No. 3, 83 (1956).
10. Maxschmidt, H., Schmidbauer, *Angew., Chem.*, **71**, No. 17, 553 (1959).

11. Schwarz, R., Schoeller, K., Ber., 91, No.10, 2103 (1958).
12. Feher, F., Lippert, K., Ber.No. 11, 2998 (1954).
13. Keeber, W.H., Post, H.W., J. Org. Chem. 21, No.5, 509 (1956).
14. Bruker, L.A., Balashova, L.D., Soborovskii, L.Z., Doklady Akademii Nauk SSSR 135, No.4, 843 (1960).
15. Coates, H., Ann.Appl. Biol., 36, 156 (1949).
16. Feher, F., Blumke, A., Ber., 90, No. 9, 1934 (1957).
17. Petrov, A.D., Doklady Akademii Nauk SSSR 93, No. 3, 199 (1953).
18. Frisch, K.C., Lyons, H., US pat. 2673210 23/III-54; C. A., 49, 401 (1950).
19. Frisch, K.C., Lyons, H., J. Am.Chem.Soc., 75, 4078 (1953).
20. Canavan, A.E., Eaborn, C., J. Chem.Soc., No. 12, 3751 (1959).
21. Brit. pat. 8/253; Referativnyi zhurnal, khimiya, p. 58897 (1960).
22. US pat. 2768193; C.A., 51, 5861 (1957).
23. US pat. 2864845; C.A., 53, 12239 (1959).
24. Ger. pat. 1086897.
25. Khimiya i tekhnologiya polimerov, No. 10, 19 (1959).
26. Chem. Eng. News, 24, 40 (1959).
27. Terent'yev, A.P., Luskina, B.M., Zhurnal analiticheskoi khimii 24, 112 (1959).
28. Terent'yev, A.P., Luskina, B.M., Syavtsillo, S.V., Zavodskaya laboratoriya 25, 288 (1959).