

UNCLASSIFIED

AD 406 258

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

63-3-6

GIID

GENERAL DYNAMICS | CONVAIR

406258

Report No. 8926-171


Material - Nickel Base Alloy - Hastelloy R-235
(Haynes Stellite Co.)

Fusion Weld Strengths

(An Abstract Report)

C. W. Alesch

19 April 1963

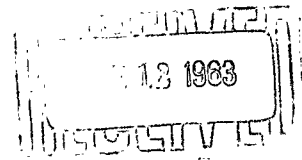

406 258

Published and Distributed
under
Contract AF33(657)-8926



GENERAL DYNAMICS | CONVAIR

MODEL
DATE

PAGE
REPORT NO.

Report No. 8926-171

Material - Nickel Base Alloy - Hastelloy R-235
(Haynes Stellite Co.)

Fusion Weld Strengths

(An Abstract Report)

Abstract:

Hastelloy R-235 nickel base alloy sheet in the thicknesses and conditions listed below was tungsten inert gas fusion but welded and tested with the following results.

	Weld Strength KSI	Joint Efficiency Percent
0.016", 10% cold worked, welded	117.6	89
0.040", solution heat treated,* welded	128.3	98
0.020", solution heat treated, aged,** welded	137.9	86
0.040", solution heat treated, welded, aged	132.0	94

* 1975°F, water quench

** 1500°F, 2 hours, air cool

Reference: Alesch, C. W., "Material - Nickel Base Alloy - Hastelloy R-235 (Haynes Stellite Co.). Fusion Weld Strengths (An Abstract Report)," General Dynamics/Convair Report 8926-171, San Diego, California, 19 April 1963. (Reference attached).



GENERAL DYNAMICS | CONVAIR

MODEL
DATE

PAGE 1
REPORT NO. 8926-171

Report No. 8926-171

Material - Nickel Base Alloy - Hastelloy R-235
(Haynes Stellite Co.)

Fusion Weld Strengths

(An Abstract Report)

Reference: Vermilyea, E. J., Green, E. D., Carr, W. L., Margitan, E.,
"Fabricability of Materials R-235, L-605, Rene 41, M-252
and J-1650 as Pertaining to Part No. 8-26054," General
Dynamics/Convair Report AMR-PR 889, San Diego, California,
April 1961.

Haynes Stellite Co. Hastelloy Alloy R-235 in the thicknesses, conditions
and strength conditions listed in Table 1 was fusion butt welded by the
tungsten inert gas method. The fusion welding schedules employed are
given in Tables 2 and 3. The strengths of the welds are given in Table 4.
"Five radiographs of fusion welded coupons were studied for porosity and
weld continuity. No porosity in or around weldments could be detected
on any of the weld specimens, and all welds exhibited good thickness
continuity." The efficiencies of the fusion welded R-235 joints were found
to be:

1. Ten per cent cold work then welded, - 89%
2. Solution heat treated then welded, - 98%
3. Solution heat treated, aged then welded, - 86%
4. Solution heat treated, welded then aged, - 94%

The solution heat treatment was done at the mill, and consisted of heating
at 1975°F and quenching in water. Aging consisted of heating at 1500°F
for 2 hours, and air cooling.

Prepared by C. W. Alesch
19 April 1963



GENERAL DYNAMICS | CONVAIR

MODEL
DATEPAGE 2
REPORT NO. 8926-171

Table 1

Mechanical Properties of R-235

Gage (in.)	Cond.	Yield Strength (.2%)	Ultimate Strength (lb)	Elong. %	Average	
					Yield Strength (lb)	Ultimate Strength (lb)
0.016	C.W.	89,700	129,200	27.0	97,000	131,900
"	"	90,100	131,600	26.9		
"	"	92,200	134,800	23.2		
0.020	A	108,600	152,400	14.5	107,100	146,500
"	A	107,400	145,100	13.0		
"	A	105,200	141,000	11.0		
0.040	A	101,100	153,400	16.4	101,000	153,100
"	A	99,400	151,200	15.8		
"	A	104,000	154,600	15.1		
0.040	S.H.T.	77,400	132,100	38.0	77,700	130,000
"	"	79,600	126,200	42.0		
"	"	76,100	131,600	37.0		

C.W. - 10% Cold Worked Material

A - Aged Material

S.H.T. - Solution Heat Treated Material

MODEL
DATEPAGE 3
REPORT NO. 8926-171

Table 2

Schedule for Welding 0.020 inch to 0.020 inch Annealed
R-235

Current:	DCSP 30 amperes
Voltage:	10 volts
Torch Speed:	15 inches/min.
Electrode:	0.040" diam. 2% thoriated tungsten
Cup Size:	#8
Back-up Gas:	argon
Flow Rate:	16 cu ft/hr
Torch Gas:	argon
Flow Rate:	16 cu ft/hr
Clamp Spacing:	0.125"
Clamp Pressure:	55 lb
Back-up Bar Material:	0.010" copper insert

Table 3

Schedule for Welding 0.040 inch to 0.040 inch Annealed
R-235

Current:	DCSP 50 amperes
Voltage:	10 volts
Torch Speed:	30 inches/min.
Electrode:	1/16" diam. 2% thoriated tungsten
Cup Size:	#8
Back-up Gas:	argon
Flow Rate:	20 cu ft/hr
Torch Gas:	17% argon - 83% Helium
Flow Rate:	50 cu ft/hr'
Clamp Spacing:	5/32"
Clamp Pressure:	80 lb
Back-up Bar Material:	0.010" copper insert



GENERAL DYNAMICS | CONVAIR

MODEL
DATEPAGE 4
REPORT NO. 8926-171Table 4
Mechanical Properties of Fusion Welded R-235

Gage in.	Cond.	Yield Strength (.2%) (lb)	Ultimate Strength (lb)	Elong. %	Average		
					Yield Strength (lb)	Ultimate Strength (lb)	Elong. %
0.016	1	91,100	120,000	6.5	88,900	117,600	5.9
"	"	86,200	120,100	7.0			"
"	"	87,900	111,900	3.5			"
"	"	90,400	118,400	6.5			
0.040	2	82,000	131,700	31.0	78,300	128,300	27.5
"	"	76,400	126,000	30.0			Adj. Weld
"	"	77,700	124,300	21.5			*P.M. Weld
"	"	77,100	131,100	27.5			Adj. Weld
0.020	4	99,400	138,100	10.4	97,900	137,900	9.9
"	"	101,000	142,700	9.9			Adj. Weld
"	"	93,400	137,300	11.2			P.M. P.M.
"	"	97,700	133,600	8.1			Weld
0.040	3	91,400	134,200	18.0	86,100	132,000	13.7
"	"	78,800	127,400	13.7			Weld
"	"	90,100	130,800	10.4			Weld
"	"	84,000	135,700	12.6			Adj. Weld

1. 10% cold worked then weld
2. Solution heat treat then weld
3. Solution heat treat, age then weld
4. Solution heat treat, weld then age

*P.M. = parent metal