

UNCLASSIFIED

AD 407 987

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

407 987
CATALOGED BY DDC
AS AD No. **407 987**

63-4-2

DMIC Report 183

February 7, 1963

**BINARY AND TERNARY PHASE DIAGRAMS
OF
COLUMBIUM, MOLYBDENUM, TANTALUM,
AND TUNGSTEN
(Supplement to DMIC Report 152)**

**DEFENSE METALS INFORMATION CENTER
Battelle Memorial Institute
Columbus 1, Ohio**

[illegible]

- Contract No. AF 33(616)-7747
Project No. 2(8-8975)

COPIES AVAILABLE FROM OTS \$.....

DMIC Report 183
February 7, 1963

BINARY AND TERNARY PHASE DIAGRAMS OF
COLUMBIUM, MOLYBDENUM, TANTALUM, AND TUNGSTEN

(Supplement to DMIC Report 152)

by

J. J. English

to

OFFICE OF THE DIRECTOR OF DEFENSE
RESEARCH AND ENGINEERING

DEFENSE METALS INFORMATION CENTER
Battelle Memorial Institute
Columbus 1, Ohio

ACKNOWLEDGMENT

The Defense Metals Information Center expresses its appreciation to Dr. E. J. Rapperport of Nuclear Metals, Inc., who furnished the phase diagrams recently determined under Air Force Contract 33(616)-7157. Westinghouse Research Laboratories and the Massachusetts Institute of Technology participated with Nuclear Metals in this work.

Information supplied by Messrs. T. D. Cooper of Wright-Patterson Air Force Base, E. K. Storm of Los Alamos Scientific Laboratory, and R. T. Dolloff of the National Carbon Company was also a welcome addition.

TABLE OF CONTENTS

	<u>Page</u>
SUMMARY	1
INTRODUCTION	3
ORGANIZATION OF THE REPORT	3
NOTES ON DIAGRAMS IN DEFENSE METALS INFORMATION CENTER REPORT 152 . . .	3

BINARY PHASE DIAGRAMS

<u>Identification Code</u>	
(5)-63	Columbium-Aluminum System
(5-1)-63	Columbium-Bismuth System
(7)-63	Columbium-Carbon System
(10)-63	Columbium-Cobalt System
(10-1)-63	Columbium-Copper System
(10-2)-63	Columbium-Gold System
(14-1)-63	Columbium-Manganese System
(16)-63	Columbium-Nickel System
(17)-63	Columbium-Nitrogen System
(18-1)-63	Columbium-Palladium System
(18-2)-63	Columbium-Platinum System
(22-1)-63	Columbium-Tellurium System
(24)-63	Columbium-Tin System
(28-1)-63	Columbium-Yttrium System
(37)-63	Molybdenum-Hafnium System
(43)-63	Molybdenum-Osmium System
(49)-63	Molybdenum-Rhodium System
(49-1)-63	Molybdenum-Ruthenium System
(55)-63	Molybdenum-Vanadium System
(55-1)-63	Molybdenum-Yttrium System
(57-1)-63	Tantalum-Aluminum System
(60)-63	Tantalum-Chromium System
(61)-63	Tantalum-Cobalt System
(61-1)-63	Tantalum-Gold System
(63-1)-63	Tantalum-Iridium System
(64-1)-63	Tantalum-Manganese System
(66)-63	Tantalum-Nitrogen System
(68-1)-63	Tantalum-Platinum System
(70-1)-63	Tantalum-Rhodium System
(73-1)-63	Tantalum-Thorium System
(77-1)-63	Tantalum-Yttrium System
(78)-63	Tantalum-Zirconium System
(80)-63	Tungsten-Boron System
(81)-63	Tungsten-Carbon System
(84-1)-63	Tungsten-Iridium System
(85-1)-63	Tungsten-Lead System
(89)-63	Tungsten-Oxygen System
(89-1)-63	Tungsten-Palladium System
(92-1)-63	Tungsten-Rhodium System
(98-1)-63	Tungsten-Yttrium System

TERNARY PHASE DIAGRAMS

(99-1)-63	Columbium-Aluminum-Nickel System ($\text{Ni}_3\text{Al-Ni}_3\text{Cb}$ System)
(99-2)-63	Columbium-Aluminum-Silicon System (1400 C)
(99-3)-63	Columbium-Aluminum-Titanium System (20 C)

TABLE OF CONTENTS
(Continued)

<u>Identification Code</u>	
(99-4)-63	Columbium-Aluminum-Titanium System (1200 C)
(99-5)-63	Columbium-Boron-Silicon System (1600 C)
(99-6)-63	Columbium Carbide-Hafnium Carbide-Uranium Carbide System (2050 C)
(99-7)-63	Columbium Carbide-Hafnium Carbide-Vanadium Carbide System (2050 C)
(99-8)-63	Columbium-Carbon-Uranium System (1700 C)
(99-9)-63	Columbium-Chromium-Nickel System (1100 C)
(99-10)-63	Columbium-Chromium-Silicon System (1000 C)
(99-11)-63	Columbium-Chromium-Silicon System (Melting Temperatures, C)
(99-12)-63	Columbium-Chromium-Vanadium System (1450 C)
(99-13)-63	Columbium-Iron-Phosphorus System (Room Temperature)
(102-1)-63	Columbium-Molybdenum-Carbon System (1900 C)
(102-2)-63	Columbium-Molybdenum-Chromium System (1000 C)
(102-3)-63	Columbium-Molybdenum-Chromium System (1200 C)
(102-4)-63	Columbium-Molybdenum-Chromium System (Liquidus Isotherms)
(105-1)-63	Columbium-Molybdenum-Uranium System (700 C, 800 C, 900 C)
(105-2)-63	Columbium-Molybdenum-Uranium System (1100 C)
(105-3)-63	Columbium-Molybdenum-Uranium System (1200 C)
(105-4)-63	Columbium-Molybdenum-Uranium System (1300 C)
(107-1)-63	Columbium-Nitrogen-Oxygen System (1500 C)
(107-2)-63	Columbium-Oxygen-Titanium System (1500 C)
(107-3)-63	Columbium-Oxygen-Zirconium System (1500 C)
(107-4)-63	Columbium-Silicon-Vanadium System (Schematic)
(116-1)-63	Columbium-Titanium-Zirconium System (Melting Temperatures, C)
(118-1)-63	Columbium-Uranium-Zirconium System (1000 C)
(122-1)-63	Columbium-Tungsten-Silicon System (Room Temperature)
(123-1)-63	Columbium-Tungsten-Zirconium System (1100 C)
(123-2)-63	Columbium-Tungsten-Zirconium System (1600 C)
(123-3)-63	Columbium-Tungsten-Zirconium System (1800 C)
(123-4)-63	Columbium-Tungsten-Zirconium System (2000 C)
(123-5)-63	Molybdenum-Aluminum-Nickel System (1175 C)
(123-6)-63	Molybdenum-Aluminum-Silicon System (1600 C)
(129-1)-63	Molybdenum-Boron-Nickel System (1000 C)
(130-1)-63	Molybdenum-Boron-Titanium System (1200 C)
(130-2)-63	Molybdenum-Boron-Titanium System (1700 C)
(148-1)-63	Molybdenum-Hafnium-Rhenium System (1600 C)
(148-2)-63	Molybdenum-Hafnium-Rhenium System (2000 C)
(148-3)-63	Molybdenum-Hafnium-Rhenium System (2400 C)
(149-1)-63	Molybdenum-Iron-Phosphorus System (Room Temperature)
(149-2)-63	Molybdenum-Iron-Silicon System (20 C)
(155-1)-63	Molybdenum-Nickel-Silicon System (1100 C)
(155-2)-63	Molybdenum-Nickel-Titanium System (1175 C)
(157-1)-63	Molybdenum-Oxygen-Titanium System (1500 C)
(157-2)-63	Molybdenum-Oxygen-Zirconium System (1500 C)
(157-3)-63	Molybdenum-Silicon-Vanadium System (800 C)
(162-1)-63	Molybdenum-Titanium-Vanadium System (Room Temperature)
(162-2)-63	Molybdenum-Titanium-Zirconium System (1500 C)
(164-1)-63	Molybdenum-Tungsten-Chromium System (1800 C)
(167-1)-63	Molybdenum-Tungsten-Silicon System (1900 C)
(167-2)-63	Molybdenum-Uranium-Vanadium System (500 C)
(167-3)-63	Molybdenum-Uranium-Vanadium System (600 C)
(167-4)-63	Molybdenum-Uranium-Vanadium System (1000 C)
(167-5)-63	Molybdenum-Uranium-Zirconium System (1000 C)
(167-6)-63	Tantalum-Aluminum-Silicon System (1400 C)
(167-7)-63	Tantalum-Boron-Nickel System (TaB ₂ -Ni)
(168-1)-63	Tantalum Carbide-Hafnium Carbide-Uranium Carbide System (2050 C)

TABLE OF CONTENTS (Continued)

Identification Code

(168-2)-63	Tantalum Carbide-Hafnium Carbide-Vanadium Carbide System (2050 C)
(169-1)-63	Tantalum-Carbon-Uranium System (1700 C)
(169-2)-63	Tantalum-Chromium-Nickel System (Solidus Temperature)
(173-1)-63	Tantalum-Cobalt-Iron System (20 C)
(173-2)-63	Tantalum-Cobalt-Iron System (1390 C)
(178-1)-63	Tantalum-Silicon-Titanium System ($TaSi_2$ - $TiSi_2$)
(178-2)-63	Tantalum-Silicon-Vanadium System (Schematic)
(186-1)-63	Tantalum-Tungsten-Silicon System ($TaSi_2$ - WSi_2)
(187-1)-63	Tungsten-Aluminum-Nickel System (800 C)
(187-2)-63	Tungsten-Aluminum-Nickel System (1200 C)
(187-3)-63	Tungsten-Aluminum-Silicon System (1500 C)
(188-1)-63	Tungsten-Boron-Thorium System (1800 C)
(194-1)-63	Tungsten-Carbon-Thorium System (1500 C)
(195-1)-63	Tungsten-Carbon-Uranium System (1000 and 1500 C)
(195-2)-63	Tungsten-Carbon-Vanadium System (1500 and 1800 C)
(195-3)-63	Tungsten-Chromium-Cobalt System (Room Temperature)
(202-1)-63	Tungsten-Chromium-Silicon System (1500 C)
(203-1)-63	Tungsten-Cobalt-Iron System (20 C)
(203-2)-63	Tungsten-Cobalt-Iron System (1400 C)
(203-3)-63	Tungsten-Germanium-Silicon System (1000 C)
(206-1)-63	Tungsten-Iron-Sulfur System (Room Temperature)
(209-1)-63	Tungsten-Silicon-Titanium System ($TiSi_2$ - WSi_2 Schematic)

BIBLIOGRAPHY

BINARY AND TERNARY PHASE DIAGRAMS OF COLUMBIUM,
MOLYBDENUM, TANTALUM, AND TUNGSTEN

SUMMARY

This report supplements DMIC Report 152 which is a compilation of binary and ternary phase diagrams of columbium, molybdenum, tantalum, and tungsten. Forty new binary and 80 new ternary diagrams are included, some of these being revised versions of the previously published diagrams. Included with each binary diagram and with some ternary diagrams is a short discussion listing terminal solubilities and crystal structures of intermediate phases. Many of the diagrams are tentative and are subject to revision as additional data become available.

INTRODUCTION

Increased interest in the refractory metals columbium, molybdenum, tantalum, and tungsten is reflected in the growing number of phase diagrams that are being determined for alloys of these metals. In DMIC Report 152, phase diagrams of alloy systems based on the four metals were assembled. Occasional supplements to DMIC Report 152 have been planned in order that up-to-date information on phase relationships in the refractory-metal-alloy systems will be available to those who need it. Data on approximately 70 additional systems have been collected by DMIC since the publication of Report 152. They are presented here along with new data on systems already reported on in DMIC 152.

It is hoped that the users of this report will supply the Defense Metals Information Center with additional phase-diagram information as it becomes available and also with any literature references that might have been inadvertently overlooked.

ORGANIZATION OF THE REPORT

The phase diagrams in this report are presented in two sections - one on binary and the other for ternary phase diagrams. Within each section, the diagrams are subdivided into four groups according to base-metal system - columbium, molybdenum, tantalum, and tungsten. The systems are then arranged in alphabetical order in these groups according to the spelling of the second element in the system. When two refractory metals occur in the same ternary system, they are listed first. For example, the columbium-molybdenum-carbon system is not listed as the columbium-carbon-molybdenum system.

Each diagram is printed on a separate page and has a code number at the lower left corner of the page to assist in relating this report with DMIC Report 152, which it supplements. As an example of the use of this code, the revised columbium-aluminum system has been given the designation (5)-63. The (5) refers to the number in the lower corner of the now out-dated columbium-aluminum system found in DMIC Report 152. The columbium-manganese system, coded (14-1)-63 is a completely new system and follows the columbium-lanthanum system, coded (14) in DMIC Report 152.

Reference numbers in this report are a continuation of the references in the bibliography of DMIC Report 152. Thus any reference of lower number than 234 (the first reference in this report) will be found in the bibliography section of DMIC Report 152.

NOTES ON DIAGRAMS IN DEFENSE METALS INFORMATION CENTER REPORT 152

The following notes refer to the phase diagrams which appeared in DMIC Report 152, April, 1961; there are no new diagrams to accompany them in this report.

Molybdenum-Aluminum System:

The compound Al_7Mo has been identified by Claire⁽³²²⁾. Al_7Mo has a monoclinic structure with $a = 5.12\text{\AA}$, $b = 13.0\text{\AA}$, $c = 13.5\text{\AA}$, and $\beta = 95$ degrees. A peritectic reaction occurs at $706 \pm 3^\circ\text{C}$ where Al_7Mo reacts with liquid to form Al_{12}Mo .

Tantalum-Chromium System:

The solubility of tantalum in chromium was reported to increase from 1.5 weight per cent at 1200°C to 8 weight per cent at 1600°C .⁽³²³⁾

Tantalum-Ruthenium System:


The μ phase is based on a CsCl B-2 type structure at 30 atomic per cent ruthenium, transforming to a distorted CsCl structure at 40 and 45 atomic per cent ruthenium.⁽³²⁴⁾

Tungsten-Hafnium System:

The previously reported value for the transformation of hafnium of $1875 \pm 20^\circ\text{C}$ has been observed to occur at $1750 \pm 20^\circ\text{C}$ by Deardorf⁽³²⁵⁾. Giessen⁽³²⁾ has verified the new value in more recent studies.


BINARY PHASE
DIAGRAMS

COLUMBIUM-ALUMINUM SYSTEM

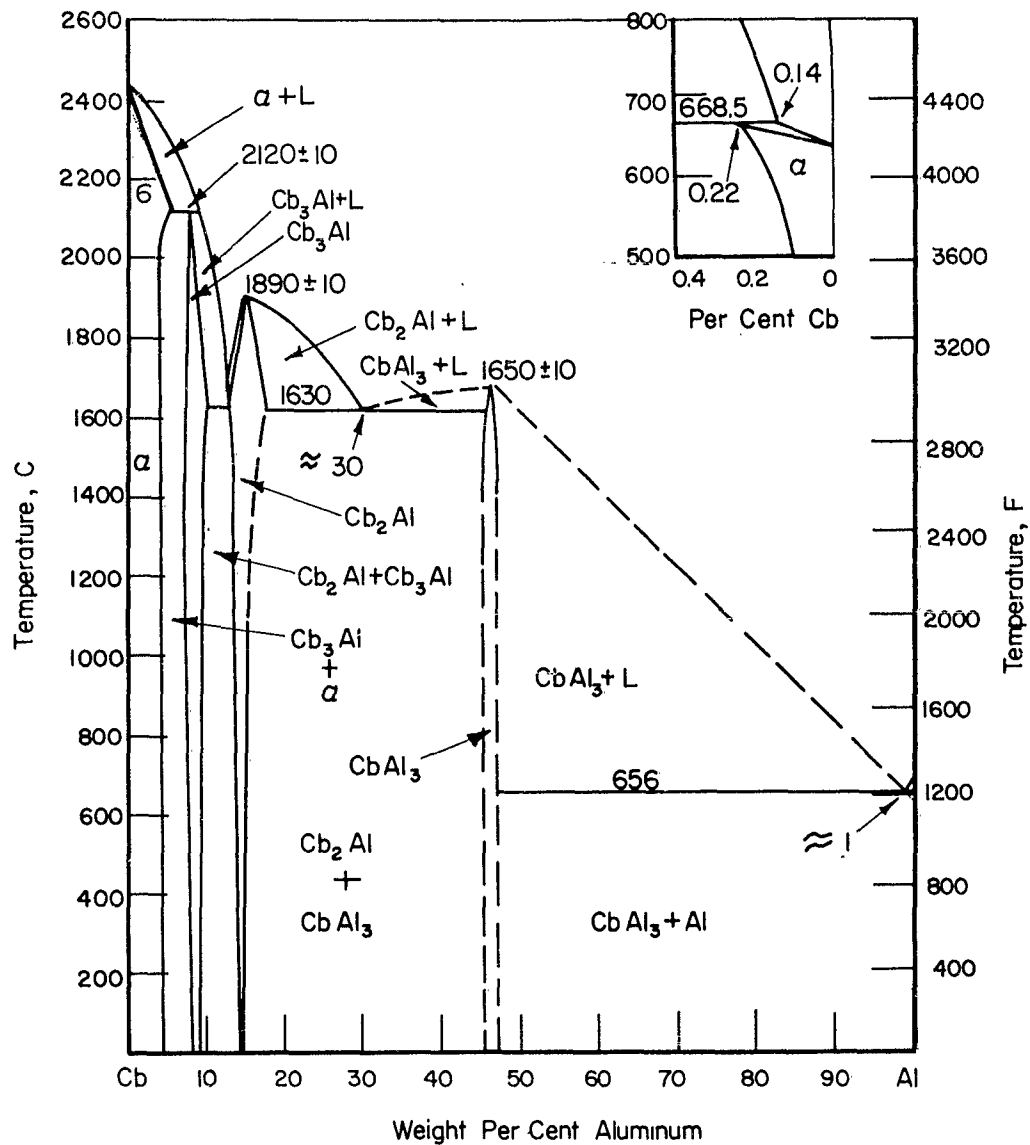


Cb₃Al has a cubic, β -tungsten type structure with $a = 5.187 \text{ \AA}$.⁽¹⁾ Cb₂Al is tetragonal (σ -phase) with $a = 5.438 \text{ \AA}$, $c = 8.601 \text{ \AA}$, and $c/a = 1.582$.⁽³⁾ Cb₂Al has been reported to form by a peritectic reaction at 1890 C⁽²³⁴⁾ instead of melting congruently, as shown above.⁽²³⁵⁾ The columbium-rich boundary of the Cb₂Al region was reported to be near 16 weight per cent aluminum (41 atomic per cent) at 1250 C.⁽²³⁶⁾ Aluminum is soluble in columbium up to 6 weight per cent at 2120 C, decreasing to 4.5 per cent at room temperature.⁽²³⁴⁾

COLUMBIUM-BISMUTH SYSTEM

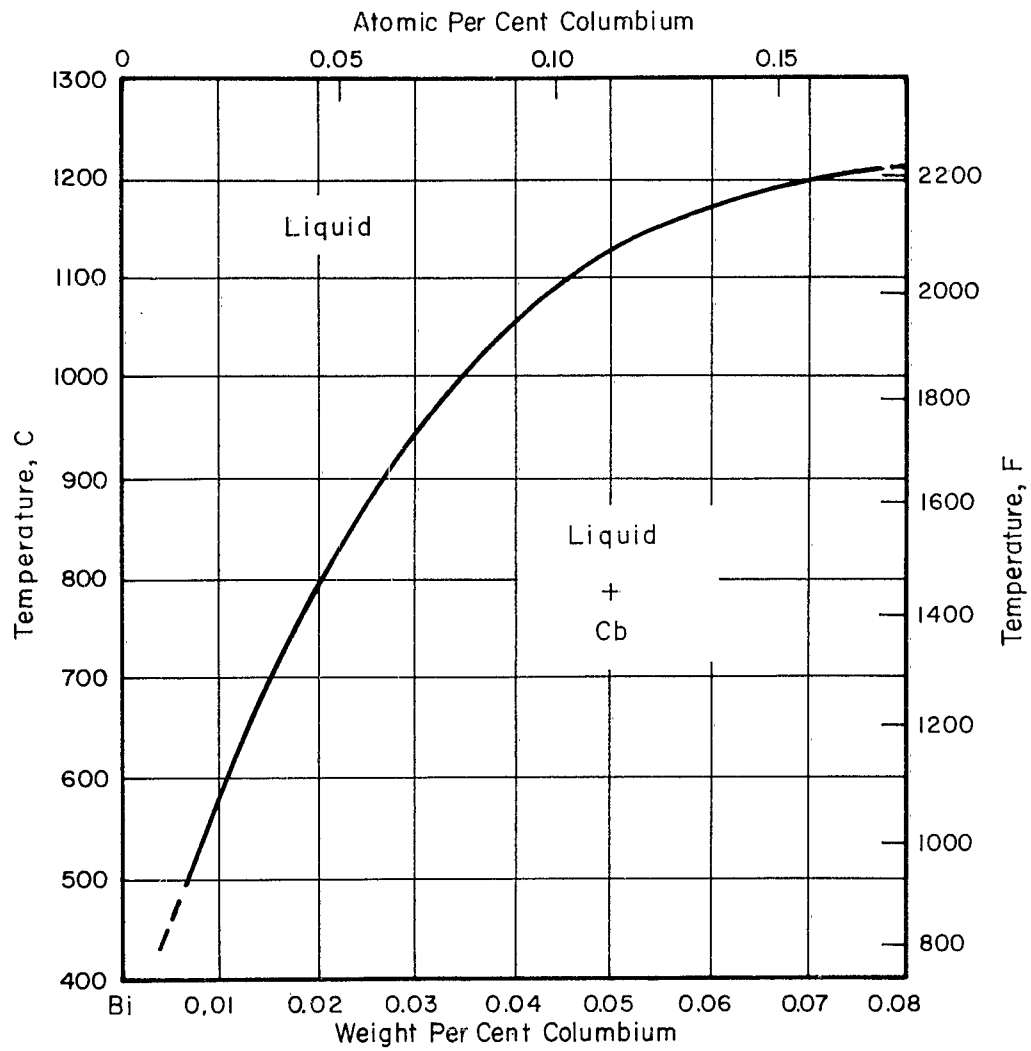


The solubility of columbiu in liquid bismuth (mp = 271 C) is shown above.⁽²³⁷⁾ There was no indication of the formation of intermetallic compounds in the system.

COLUMBIUM-CARBON SYSTEM

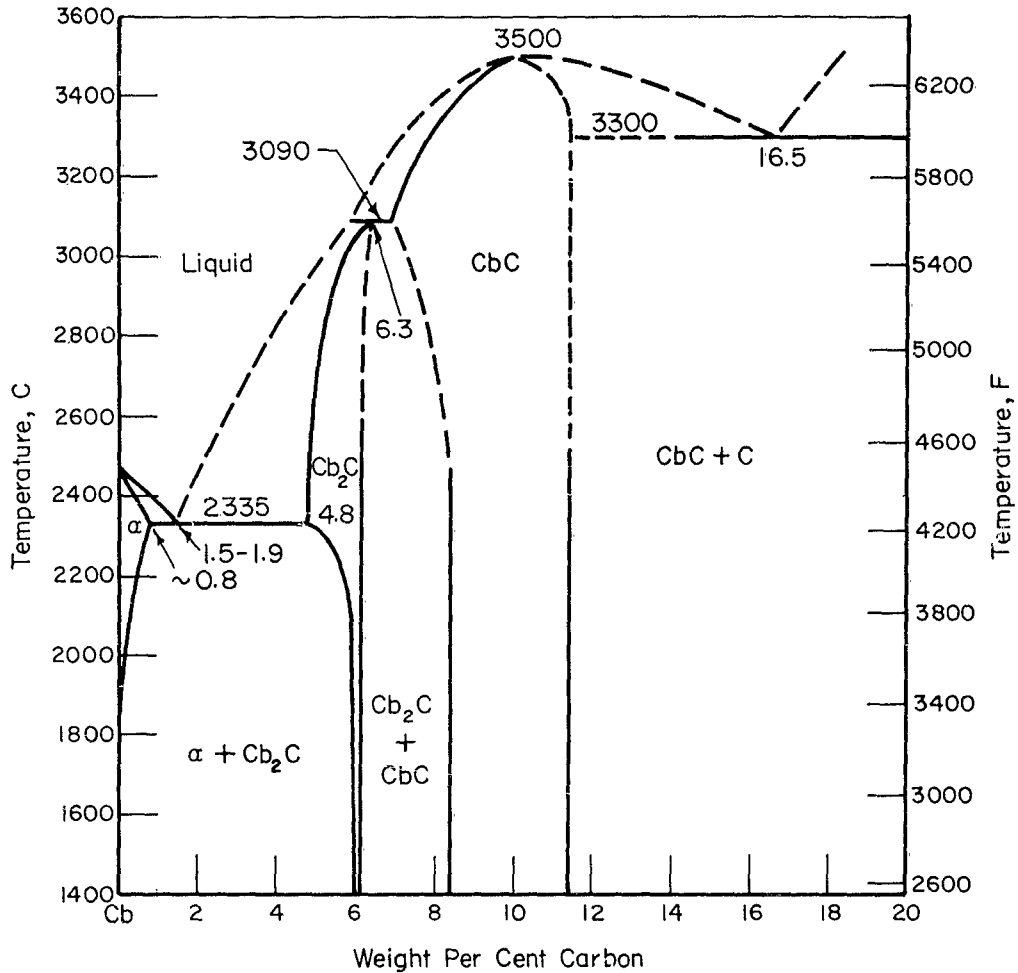


Cb₂C has a hexagonal structure with the single-phase region ranging from CbC_{0.39} at the eutectic temperature to a maximum of CbC_{0.52} at the peritectic temperature.⁽²³⁸⁾ CbC is face-centered cubic with $a = 4.470$ at 25°C.^(8,9,238) The maximum melting point of CbC occurs at a composition of CbC_{0.86}. Beyond the maximum melting point, the solidus drops to meet the CbC-C eutectic at 3300°C and 60.5 atomic per cent carbon.⁽²³⁹⁾ The maximum solubility of carbon in columbium is 0.7 to 0.8 weight per cent.^(10,239)

COLUMBIUM-COBALT SYSTEM

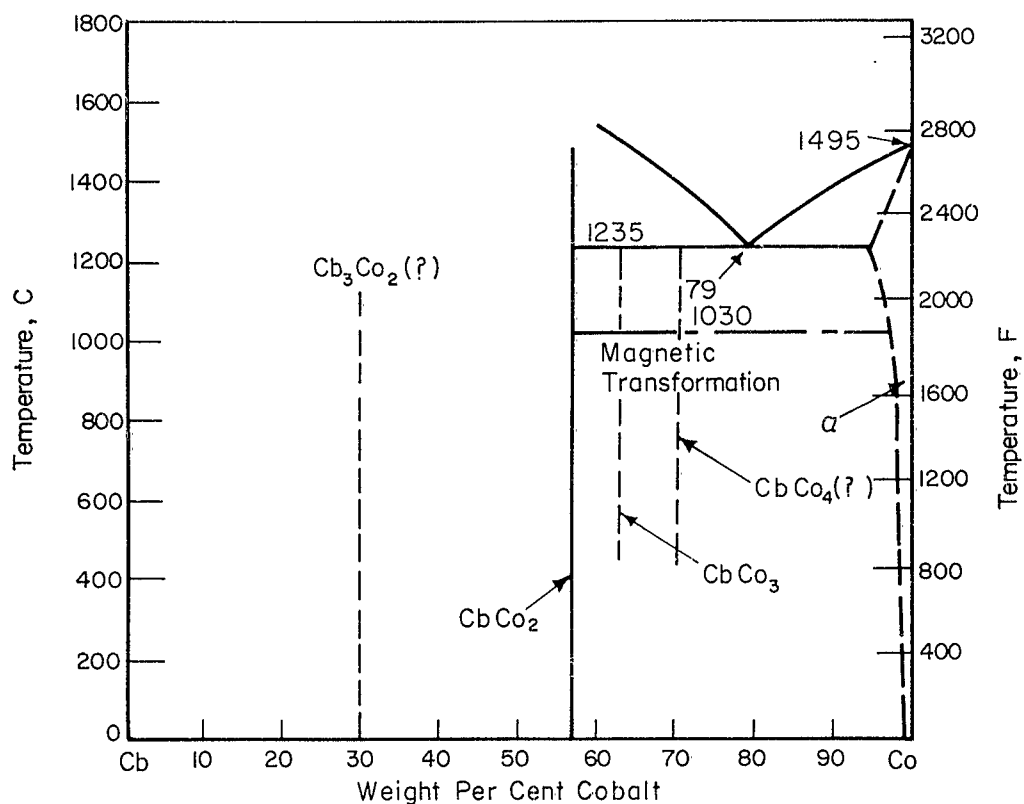


CbCo₂ is believed to exist in two modifications. One is at 33.3 atomic per cent columbium, and has a cubic MgCu₂ (C15) type of structure with $a = 6.758 \text{ \AA}$; the second structure exists around 27 atomic per cent columbium and has the MgNi₂ (C36) type of structure with $a = 4.738 \text{ \AA}$, $c = 15.46 \text{ \AA}$, and $c/2a = 1.631$.^(14, 15, 16) Two additional phases were reported to exist at 1100 C, Cb₃Co₂ and CbCo₄.⁽²⁴¹⁾ The solubility of columbium in cobalt is about 5 weight per cent at 1100 C.⁽²⁴⁰⁾

COLUMBIUM-COPPER SYSTEM

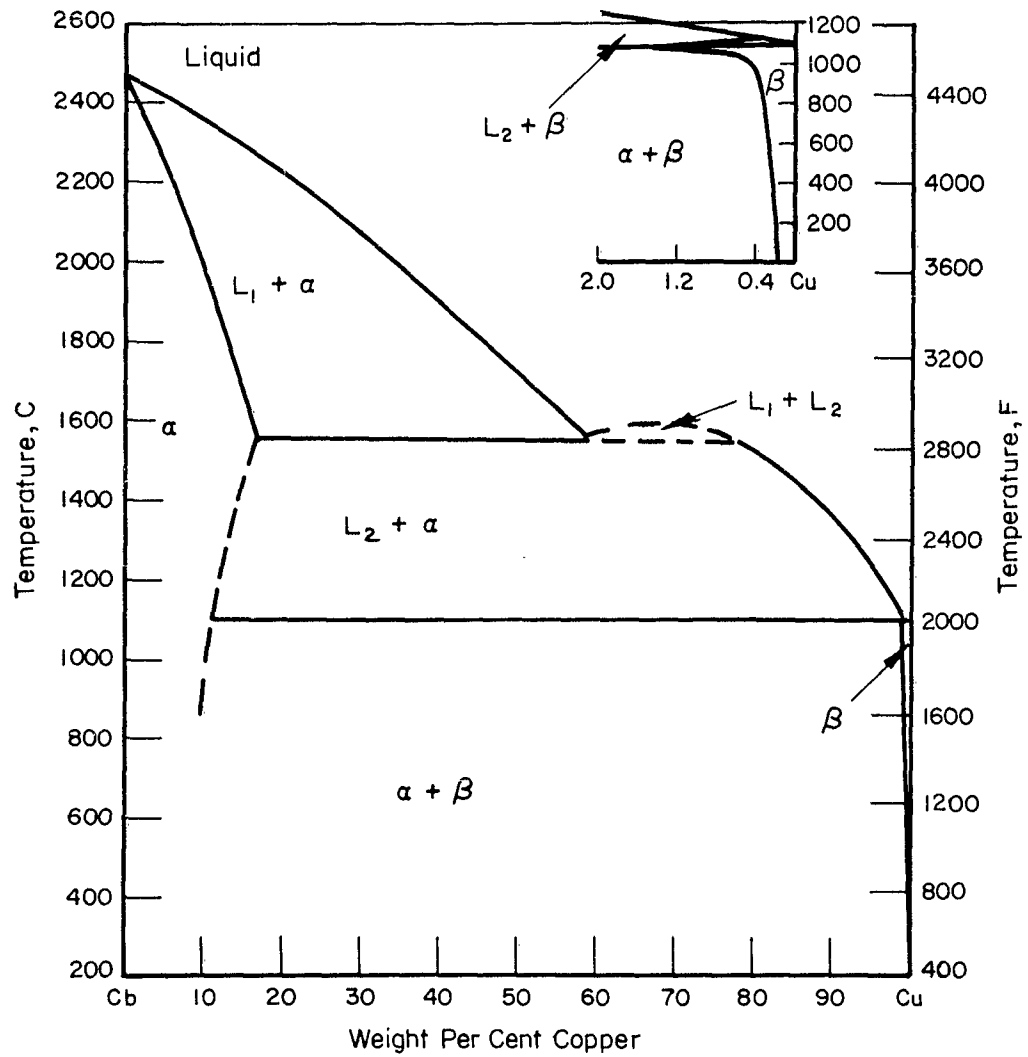


No intermetallic compounds are found in the columbium-copper system.⁽²⁴¹⁾

COLUMBIUM-GOLD SYSTEM

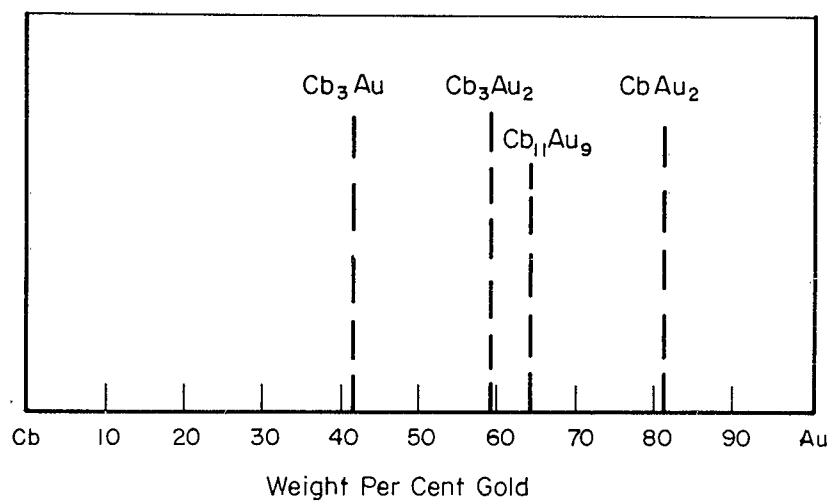


Cb_3Au is a cubic Cr_3O -type compound with $a = 5.20$ kX. Cb_3Au_2 has a D_{4h}^{17} -I4/m structure with $a = 3.37$ kX and $c = 5.3.03$ kX. $\text{Cb}_{11}\text{Au}_9$ possesses a β -manganese structure with $a = 7.04$ kX. The structure of CbAu_2 is of the B_2Al type with $a = 4.60$ kX and $c = 2.71$ kX.⁽²⁴²⁾

COLUMBIUM-MANGANESE SYSTEM

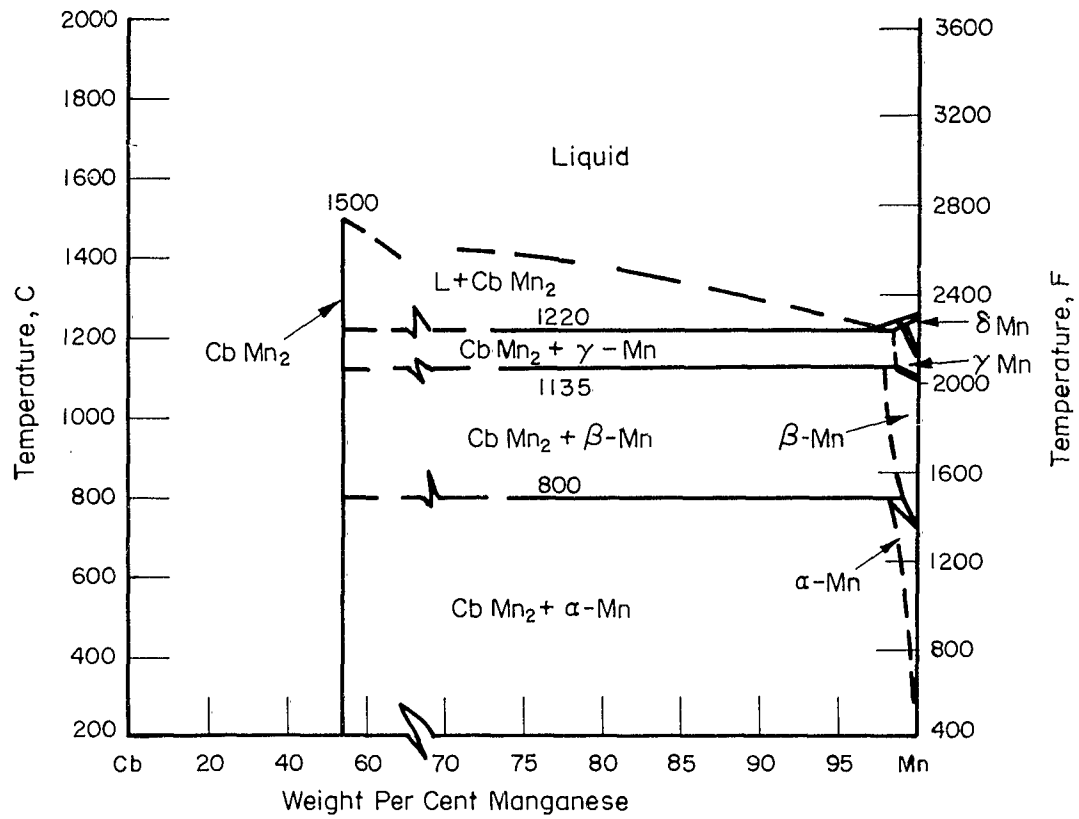


CbMn₂ has a hexagonal MgZn₂-type structure with $a = 4.881 \text{ kX}$, $c = 7.953 \text{ kX}$, and $c/a = 1.629$. Alloys containing less than 2 weight per cent columbium transform from γ -manganese to δ -manganese by a peritectic reaction near the melting point. (299)

COLUMBIUM-NICKEL SYSTEM

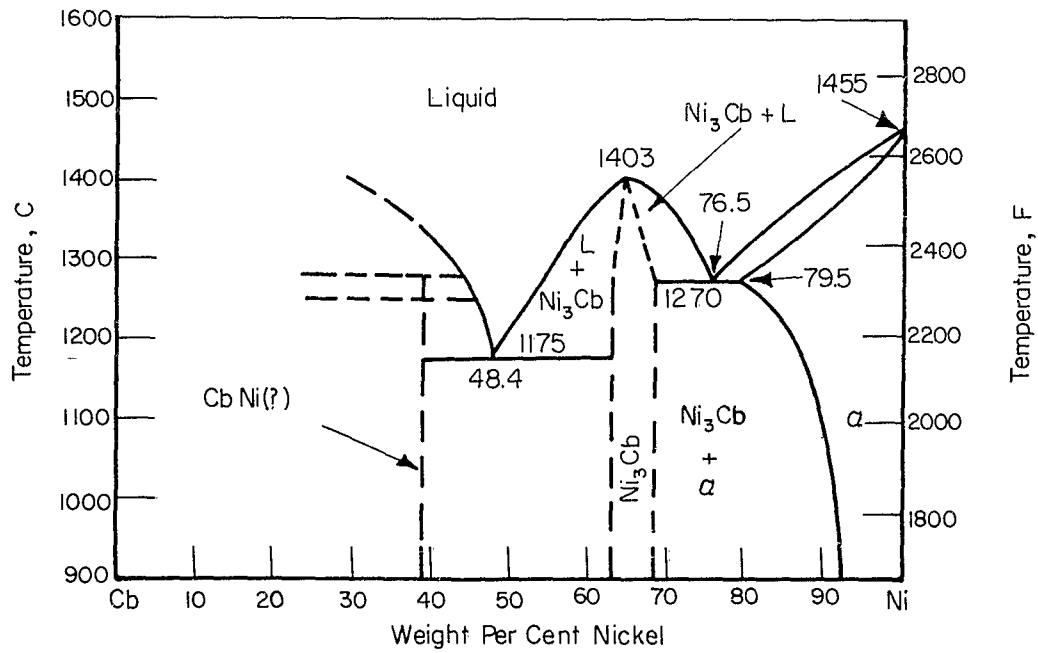


CbNi₃ has an orthorhombic TiCu₃-type structure with lattice parameters: $a = 5.10 \text{ kX}$, $b = 4.55 \text{ kX}$, and $c = 4.25 \text{ kX}$.⁽²³⁾ The solubility of columbium in nickel is approximately 15 weight per cent at 1250 C. The solubility of nickel in columbium is less than 5 weight per cent.⁽²⁴⁾ The diagram was constructed from the data prepared by Pogodin and Selekman.⁽²⁵⁾

COLUMBIUM-NITROGEN SYSTEM

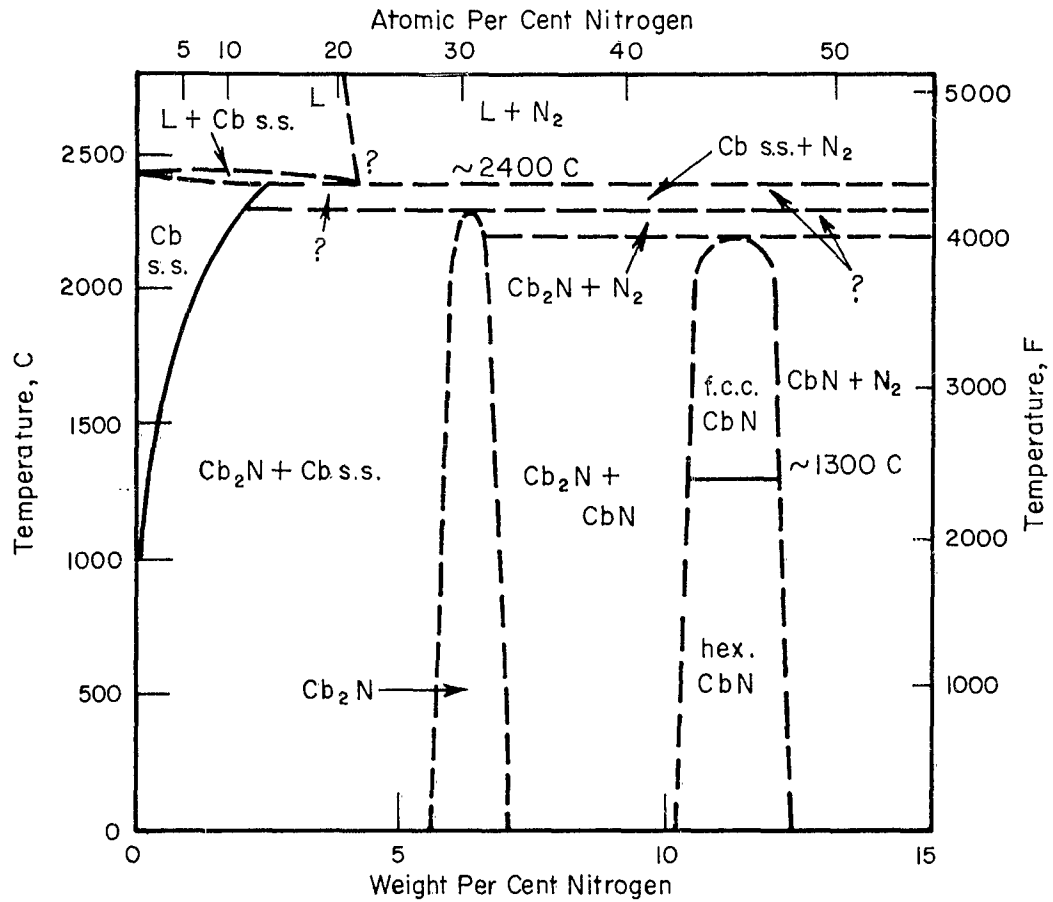


Cb₂N is a close-packed-hexagonal structure, with the lattice parameters varying between $a = 3.057 \text{ \AA}$, $c = 4.957 \text{ \AA}$ ($c/a = 1.622$) and $a = 3.050 \text{ \AA}$, $c = 5.005 \text{ \AA}$ ($c/a = 1.641$).^(21, 243) The high-temperature structure of CbN is face-centered cubic with $a = 4.386$ to $4.394 \text{ \AA}$.⁽²⁴³⁾ The low-temperature structure of CbN is hexagonal, with the lattice parameters varying between $a = 2.953 \text{ \AA}$, $c = 11.243 \text{ \AA}$ ($c/a = 3.804$) and $a = 2.953 \text{ \AA}$, $c = 11.257 \text{ \AA}$ ($c/a = 3.813$).^(22, 243) The solubility of nitrogen in columbium is 0.25 weight per cent at 1200 C and 2.5 weight per cent at 2400 C.

COLUMBIUM-PALLADIUM SYSTEM

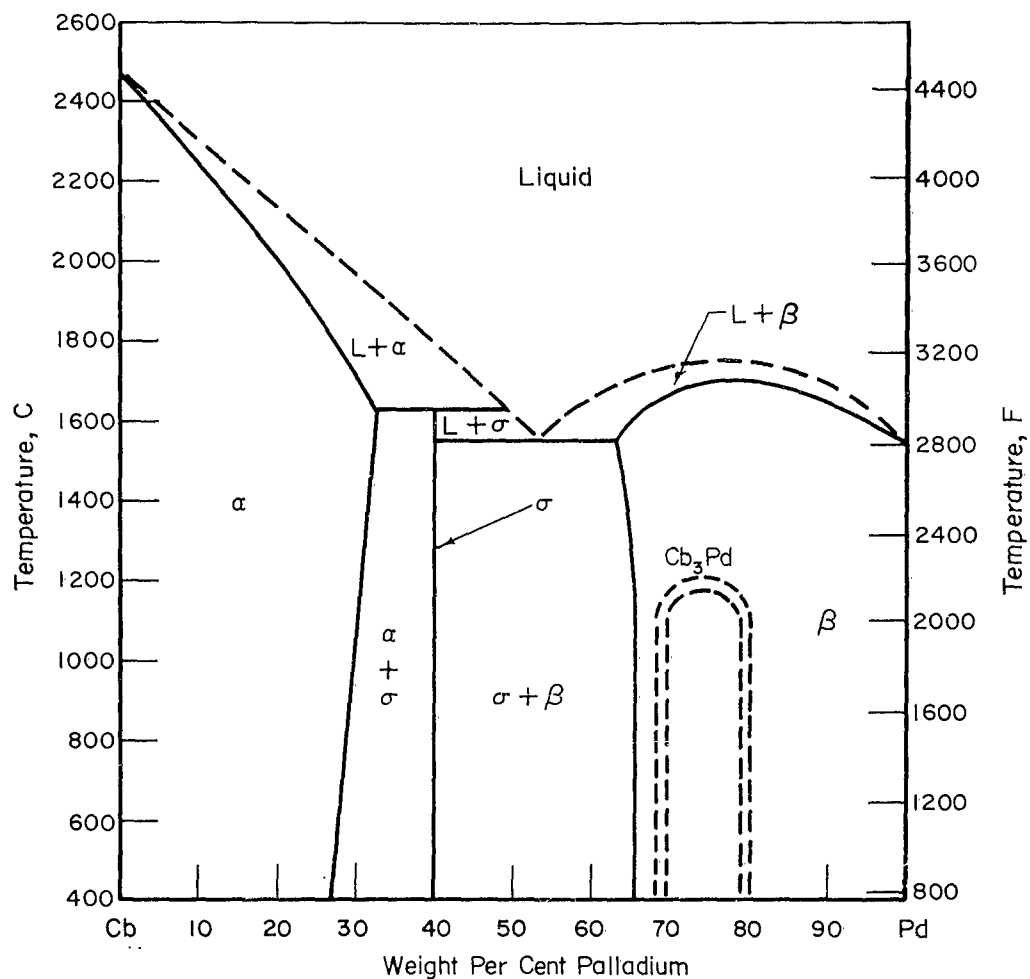


One intermediate phase having a tetragonal σ -phase structure, with $a = 0.89 \text{ \AA}$, $c = 5.11 \text{ \AA}$, $c/a = 0.52$, was reported.⁽³⁰⁾ An ordered structure is possibly present at the Cb_3Pd composition.⁽²⁴⁴⁾

COLUMBIUM-PLATINUM SYSTEM

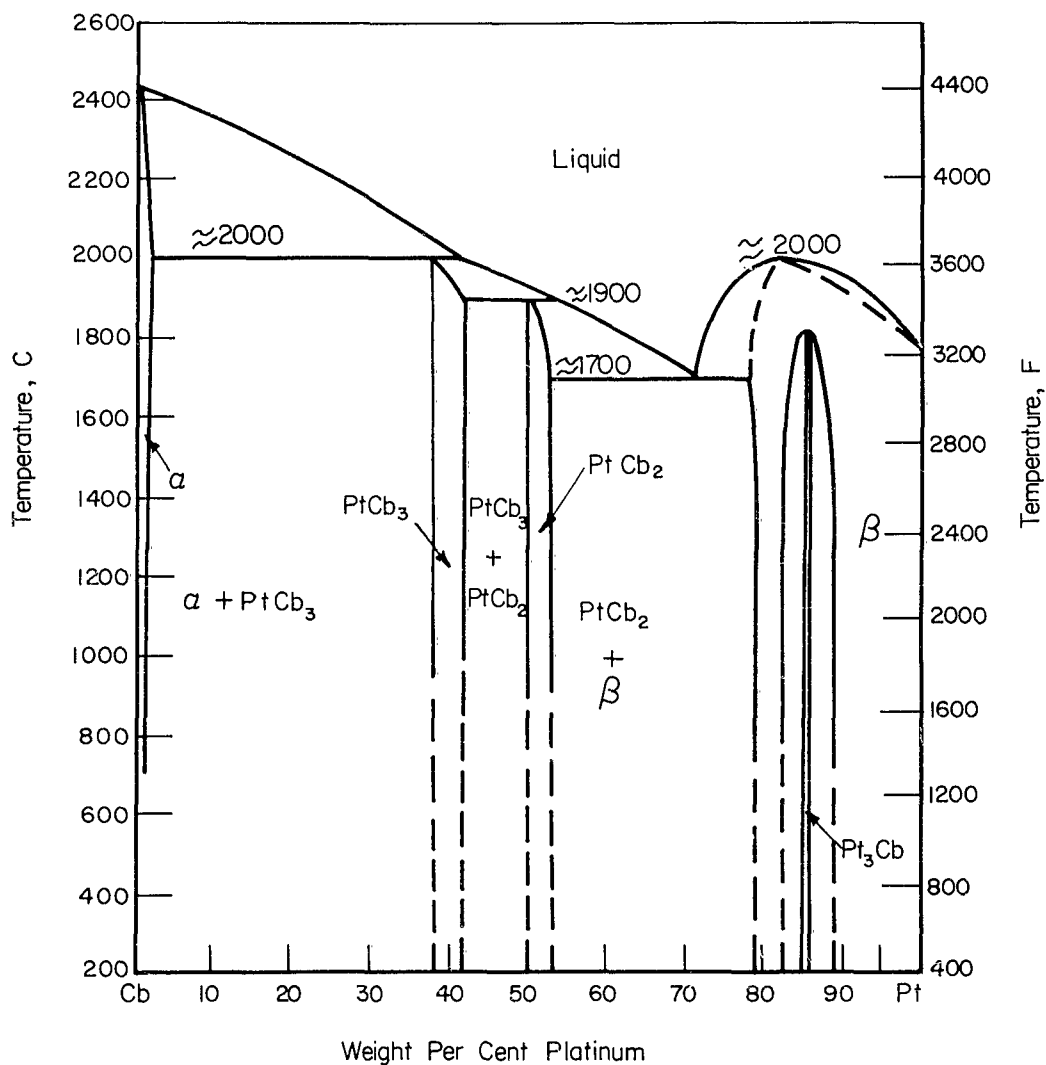


$PtCb_3$ has a β -tungsten type structure with its lattice parameters increasing from 5.137 to 5.156 kX with increasing columbium content. $PtCb_2$ has a tetragonal lattice and forms a eutectic with β at 55 atomic per cent platinum. Columbium is soluble in platinum up to 36 atomic per cent (21 weight per cent). The solubility limit of platinum in columbium is less than 1 atomic per cent. Pt_3Cb forms a superlattice near 1800 C.⁽²⁴⁵⁾

COLUMBIUM-TELLURIUM SYSTEM

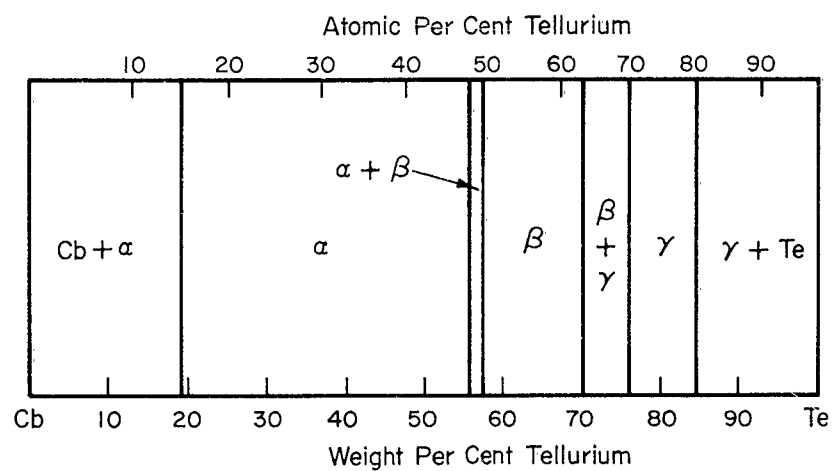


The above phase relationships are for 20 C. ⁽²⁴⁶⁾

COLUMBIUM-TIN SYSTEM

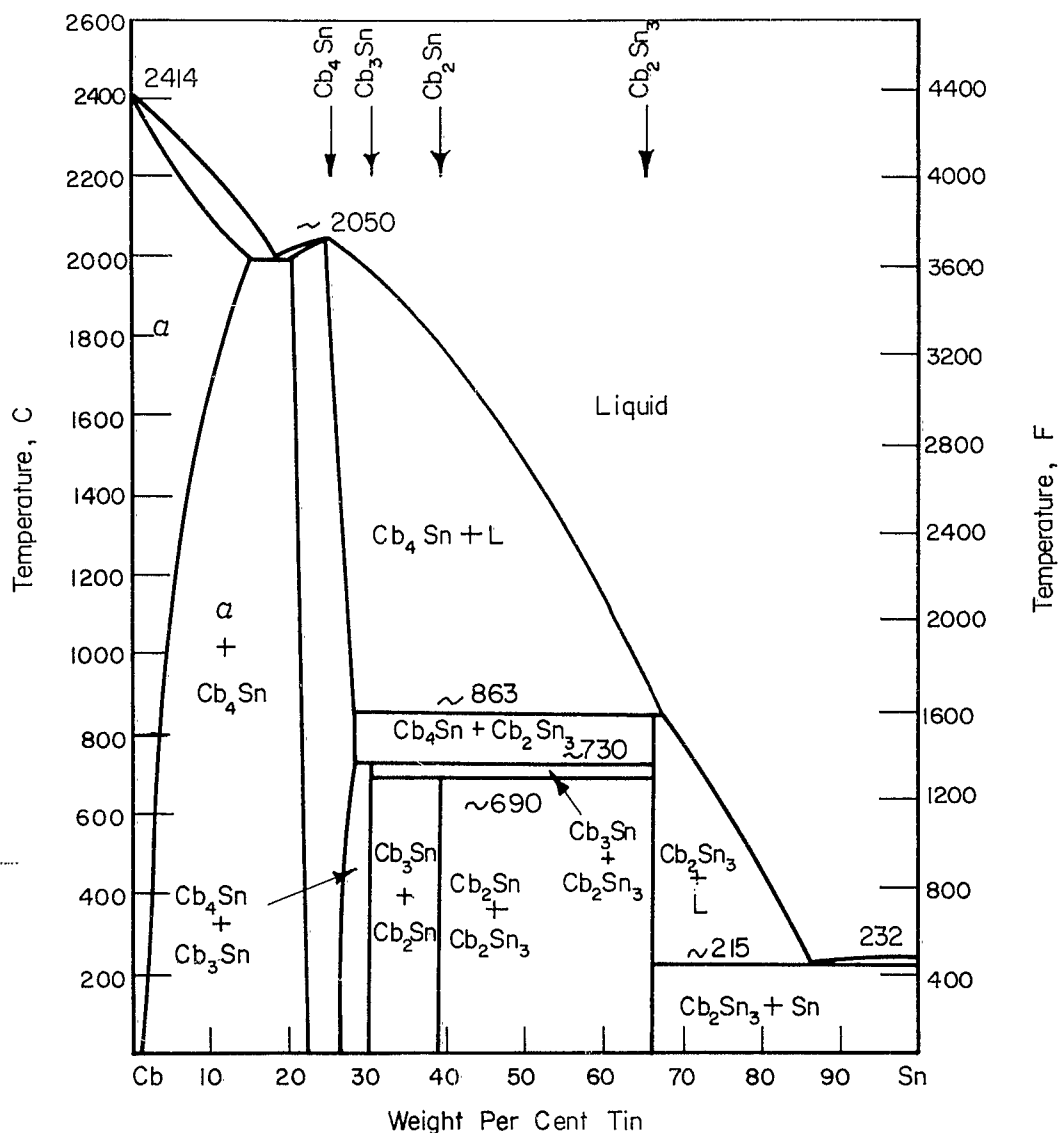


Cb_3Sn is a β -tungsten type structure with $a = 5.29 \text{ \AA}$.^(38,39) Agafonova, et al., determined the solid solubility of tin in columbium as 9.7 weight per cent at room temperature, increasing to 14 per cent at 2000 C. The solubility of columbium in tin is less than 0.1 weight per cent at the melting point of tin.⁽³⁸⁾ L. L. Wyman, et al., identified three additional phases in the system, Cb_4Sn , Cb_2Sn , and Cb_2Sn_3 . A slightly higher solid solubility of tin in columbium was also indicated. The modified diagram was suggested by Wyman, et al.⁽³⁰⁴⁾

COLUMBIUM-YTTRIUM SYSTEM

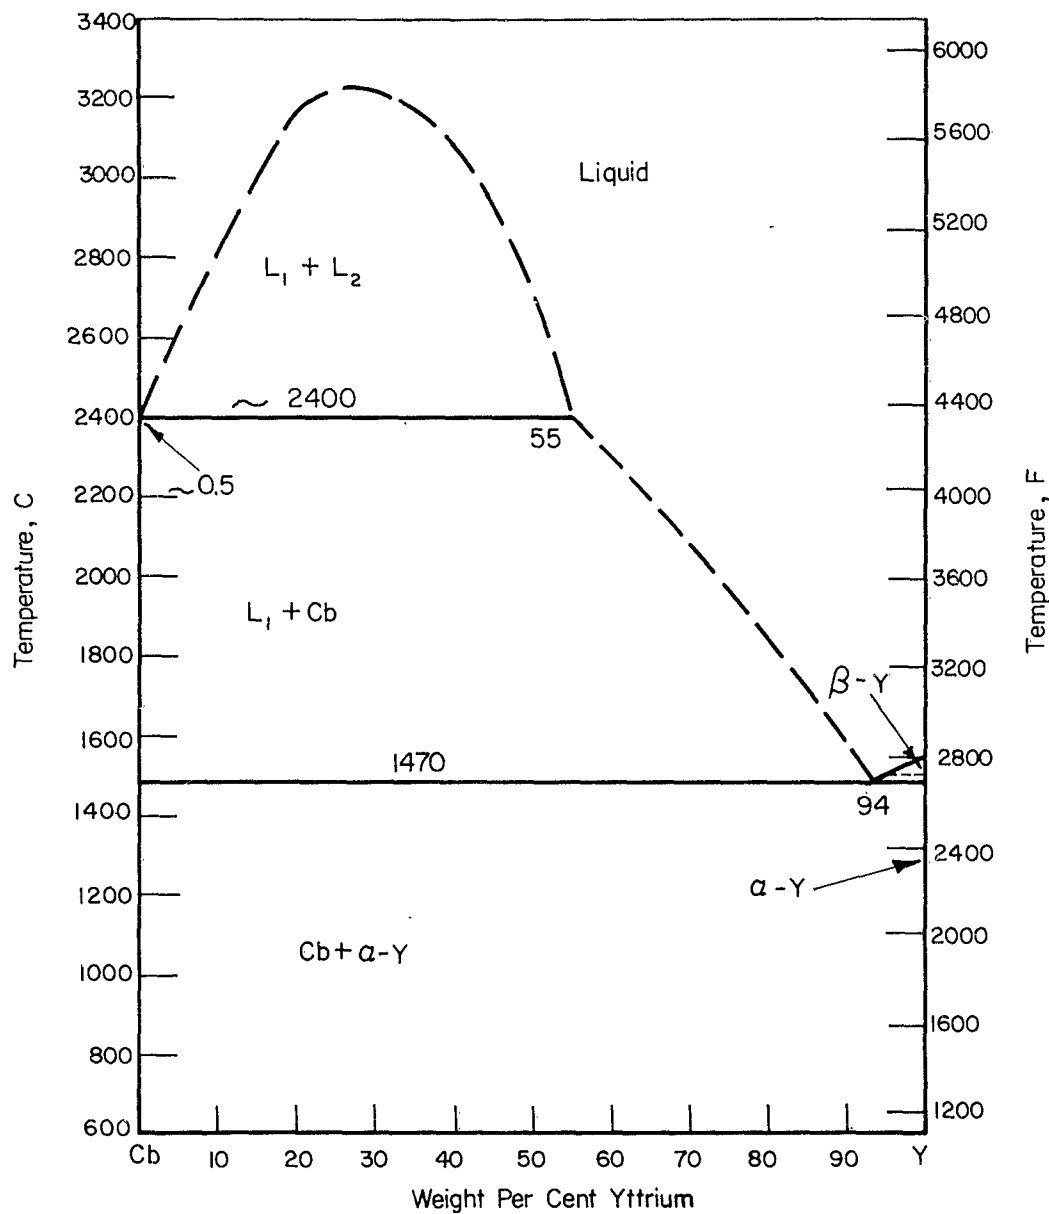


The maximum solubility of yttrium in columbium is less than 0.1 weight per cent, and the maximum solubility of columbium in yttrium is 0.2 ± 0.1 weight per cent.^(247, 248, 249) An inverse peritectic reaction in the yttrium-rich region is postulated for this system.⁽²⁴⁹⁾

MOLYBDENUM-HAFNIUM SYSTEM

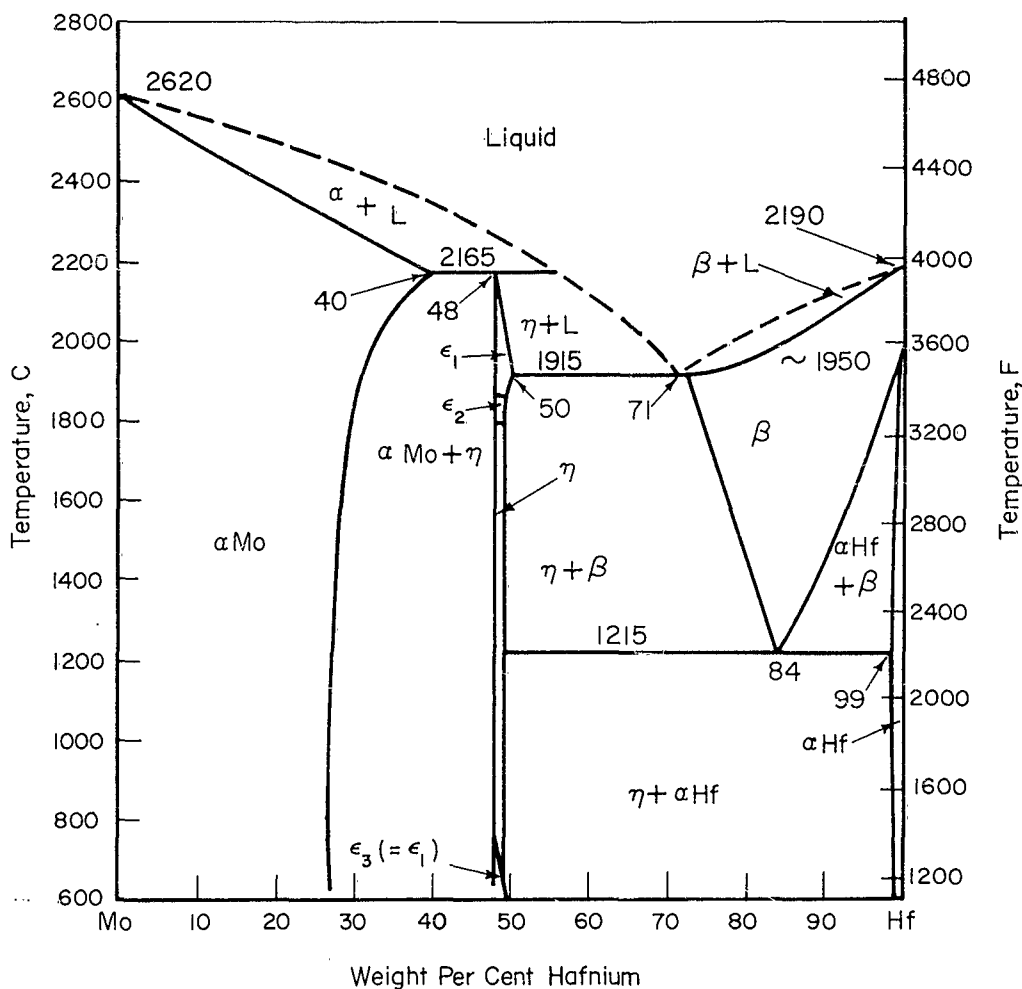


ϵ_1 (Mo_2Hf) is a hexagonal Laves phase of the C36-MgNi_2 type, with $a = 5.341 \text{ \AA}$, $c = 17.347 \text{ \AA}$, and $c/a = 3.248$. Between 1850 and 1816 C, ϵ_1 changes to ϵ_2 which is intermediate between the C36-MgNi_2 and C14-MgZn_2 structures; the lattice parameters are $a = 5.349 \text{ \AA}$, $c = 17.490 \text{ \AA}$, and $c/a = 3.270$. Upon annealing at 1752 C, ϵ_2 transforms to the cubic C15-MgCu_2 modification η with $a = 7.560 \text{ \AA}$. Annealing Mo_2Hf at 700 C for 2 weeks and quenching transforms the structure to the original C36-MgNi_2 structure of the ϵ_1 high-temperature phase. (78, 250)

MOLYBDENUM-OSMIUM SYSTEM

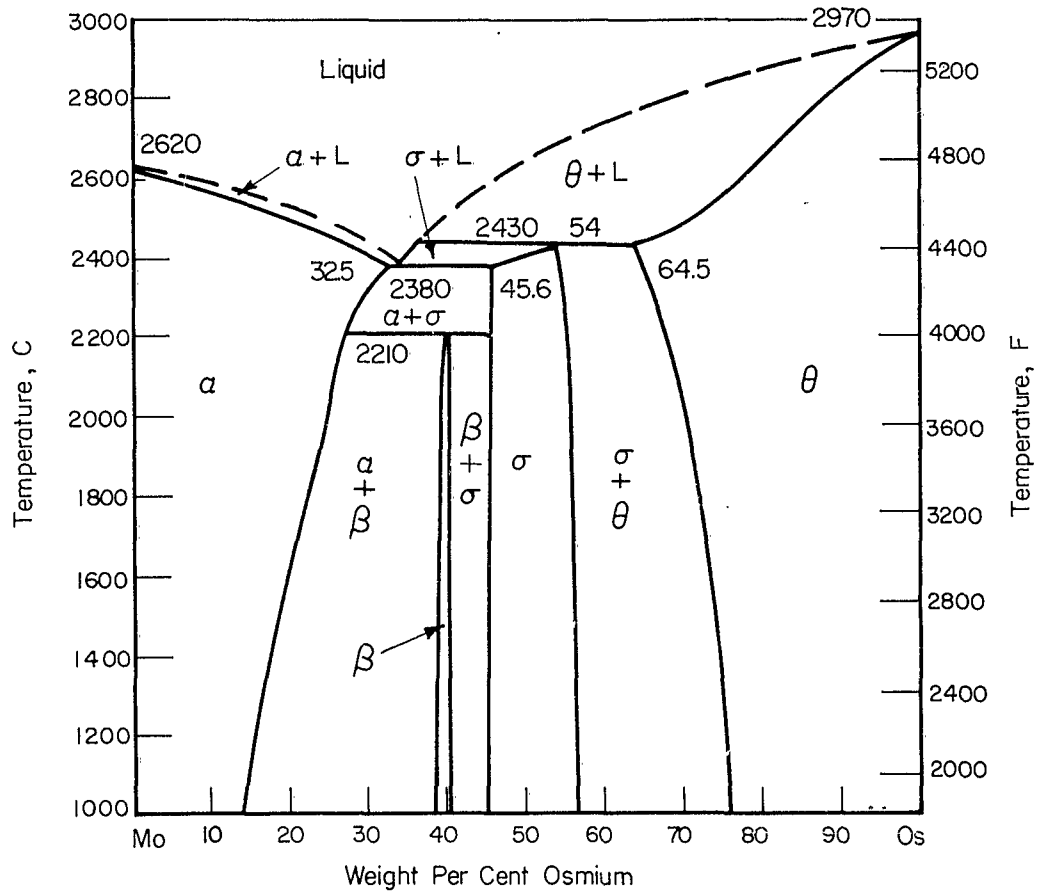


The β -Mo₃Os phase has a β -tungsten A15 type structure with the lattice parameters ranging from 4.971 Å at 24.5 atomic per cent osmium to 4.969 Å at 25 atomic per cent. The σ -phase is typical of σ -FeCe which has the atomic arrangement of tetragonal β -uranium; the lattice parameters decrease with the addition of osmium from $a = 9.632$ Å and $c = 4.950$ Å at 30 atomic per cent osmium (46 weight per cent) to $a = 9.613$ and $c = 4.934$ Å at 37.5 atomic per cent osmium (55 weight per cent). Osmium is soluble in molybdenum up to 19.5 atomic per cent (32.5 weight per cent) at 2380°C, decreasing to 7.0 atomic per cent (14 weight per cent) at 1000°C. Molybdenum dissolves in osmium up to 52 atomic per cent (35.5 weight per cent) at 2430°C, decreasing to 40 atomic per cent (25 weight per cent) at 1100°C.⁽²⁵⁰⁾

MOLYBDENUM-RHODIUM SYSTEM

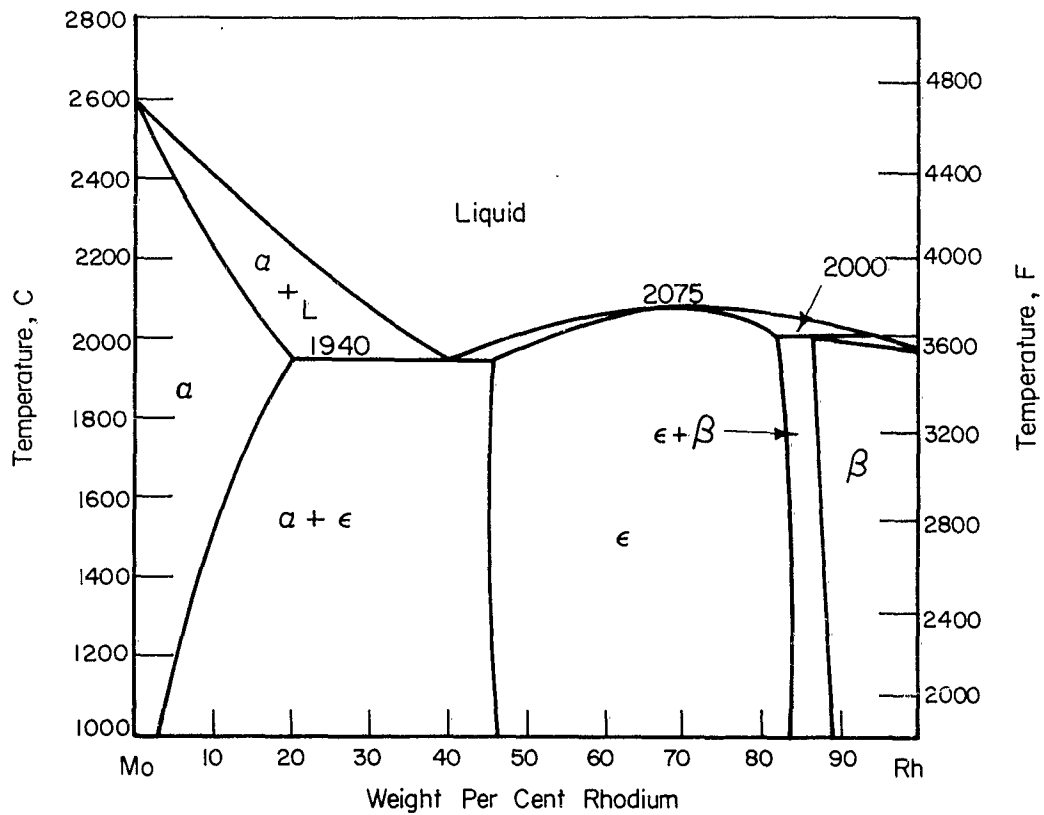


The ϵ -phase is close-packed hexagonal with $a = 2.740$ kX, $c = 4.380$ kX, and $c/a = 1.5999$ at 60 weight per cent rhodium.^(90,92) The maximum melting point for ϵ corresponds to the approximate composition MoRh_2 . Rhodium is soluble in molybdenum up to 21 weight per cent at 1940 C, decreasing to less than 3 weight per cent at 1100 C.⁽⁹⁰⁾ Rhodium can dissolve about 14 weight per cent (15 atomic per cent) molybdenum near 2000 C.⁽³⁰⁷⁾

MOLYBDENUM-RUTHENIUM SYSTEM

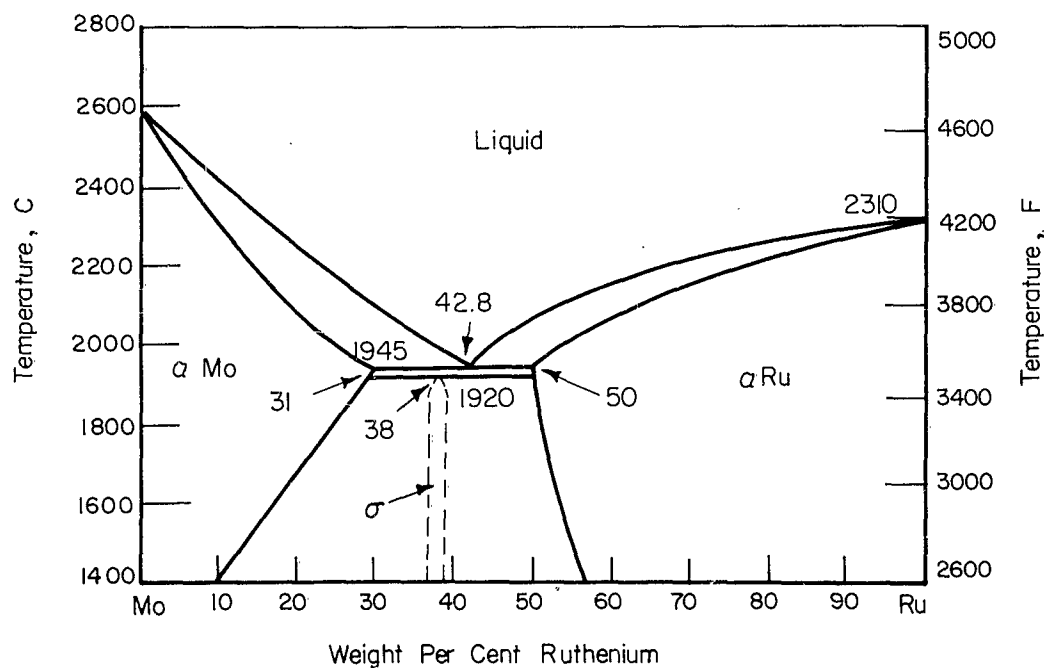


The σ -phase forms by a peritectoid reaction at 1920 C; the lattice parameters are $a = 9.538 \text{ kX}$, $c = 4.925 \text{ kX}$, and $c/a = 0.516$. The composition Mo_5Ru_3 is included in the composition range of the σ -phase. The solubility of ruthenium in molybdenum decreases rapidly from 31 weight per cent at 1945 C to 14 weight per cent at 1500 C. (251)

MOLYBDENUM-VANADIUM SYSTEM

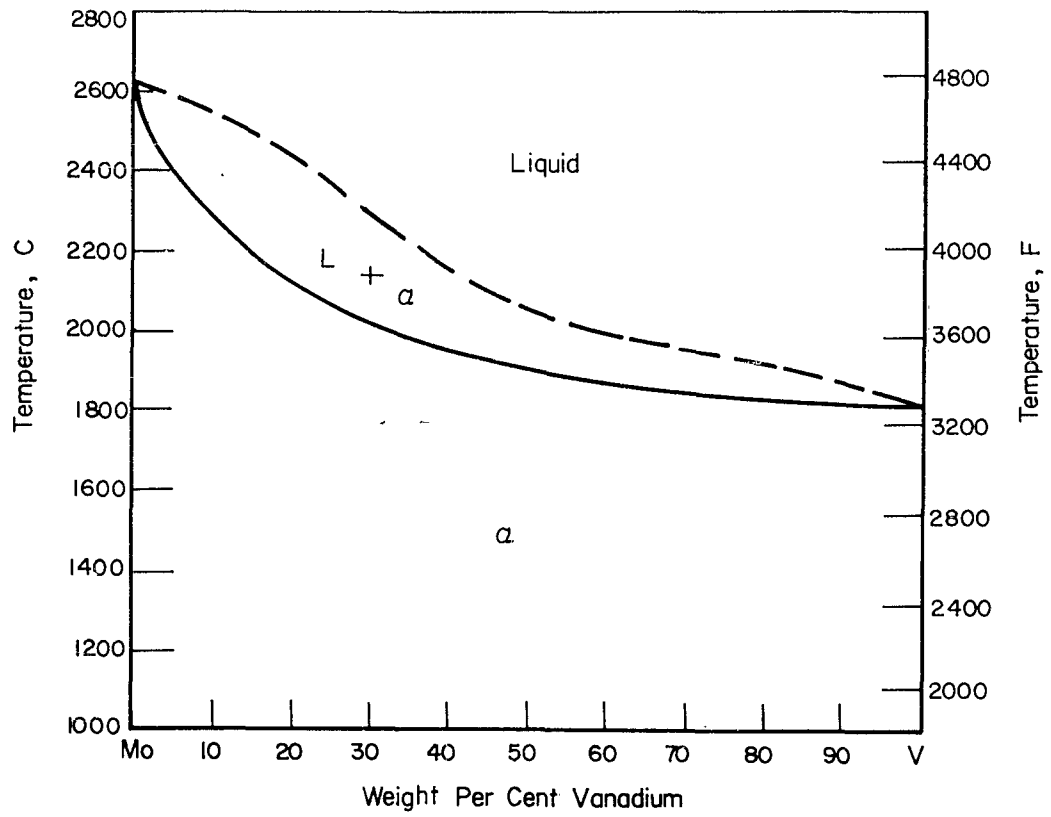


The molybdenum-vanadium system forms a continuous series of solid solutions.⁽³¹¹⁾

MOLYBDENUM-YTTRIUM SYSTEM

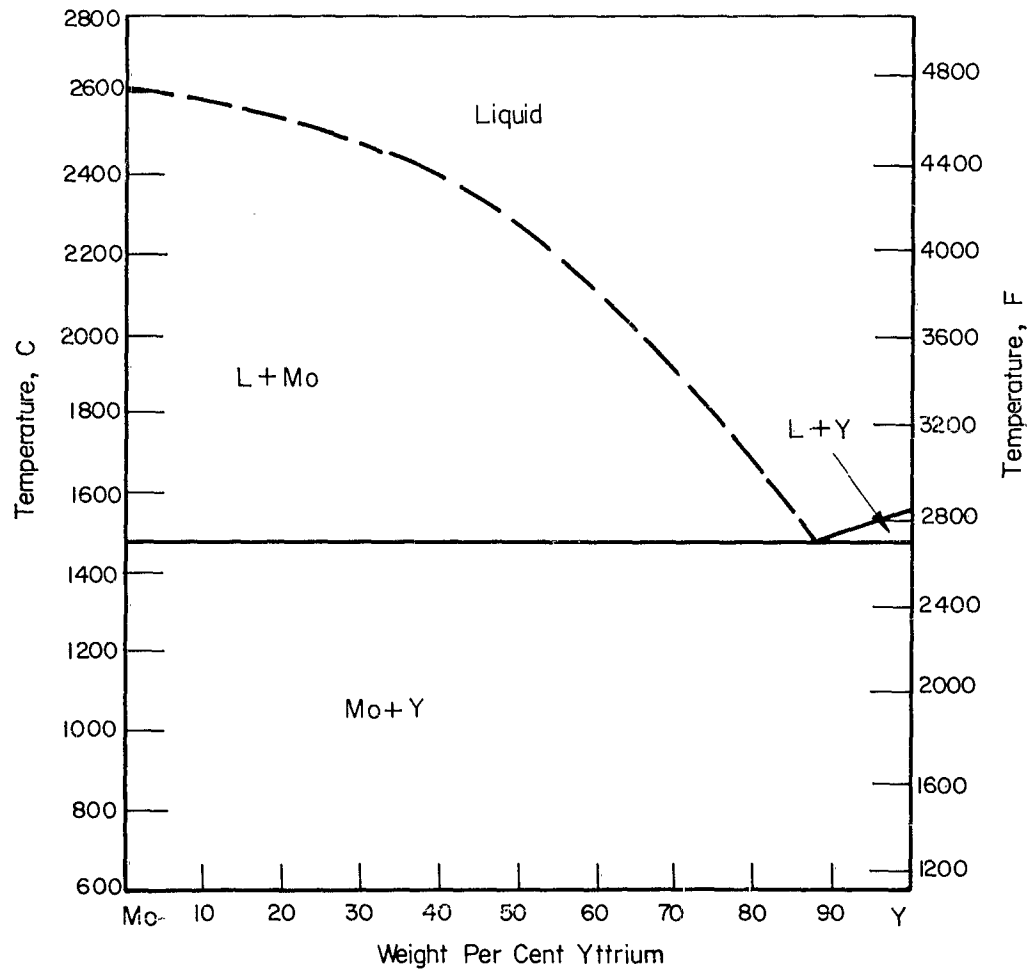


Terminal solubilities are probably less than 1 atomic per cent.^(247, 248)

TANTALUM-ALUMINUM SYSTEM

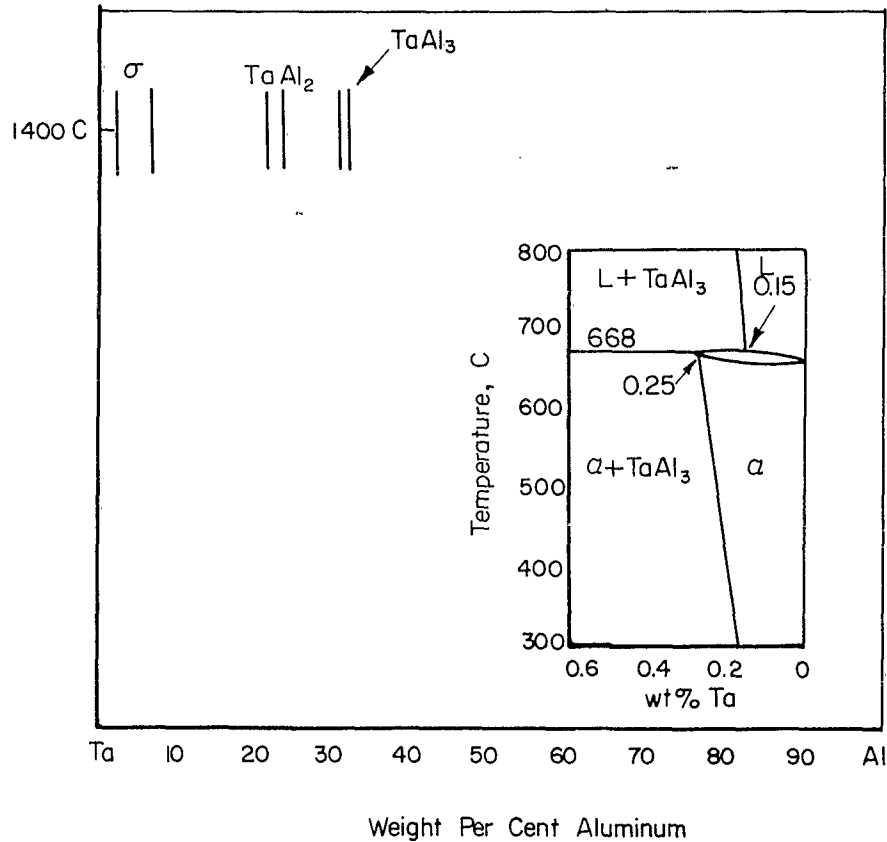


Three intermetallic compounds are present in the tantalum-aluminum system. $TaAl_3$ is isomorphous to $CbAl_3$, having a tetragonal structure with $a = 5.42 \text{ kX}$ and $c = 8.52 \text{ kX}$. A compound in the vicinity of 65 atomic per cent aluminum, possibly $TaAl_2$, exhibits a structure similar to the $ZrAl_3$ or $ZrSi_2$.⁽²⁶⁶⁾ Ta_2Al is a tetragonal σ -type phase with $a = 9.828 \text{ \AA}$, $c = 5.232 \text{ \AA}$, and $c/a = 0.532$.⁽²⁶⁷⁾ The above intermediate phase boundaries are for 1400 C.⁽²⁶⁶⁾ The solubility of tantalum in aluminum was determined by Glazov.⁽³¹⁰⁾

TANTALUM-CHROMIUM SYSTEM

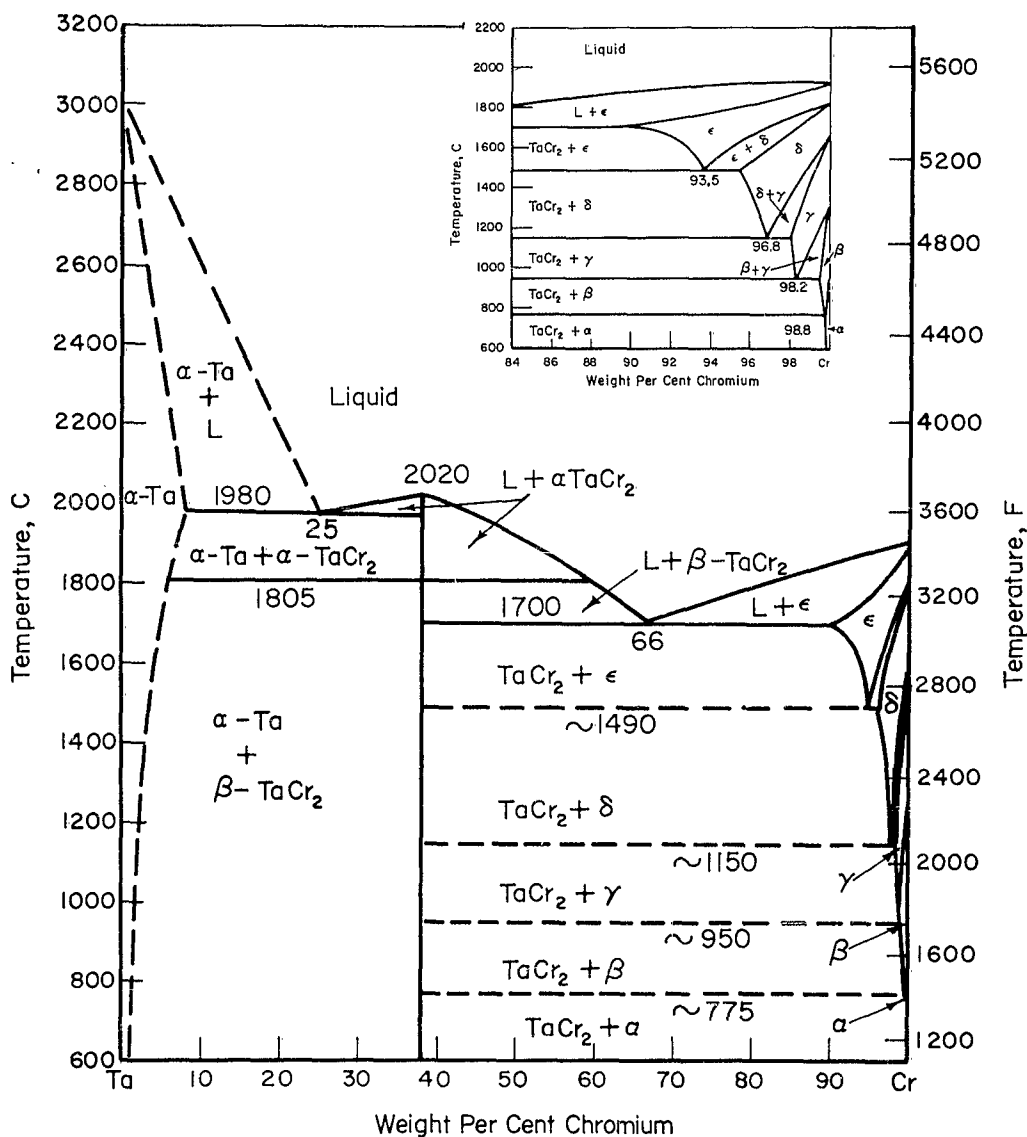


Duwez and Martens⁽¹²³⁾ reported that TaCr₂ has a polymorphic transformation between 1375 and 1590 C from the low-temperature cubic structure (MgCu₂-type with $a = 6.961$ Å) to the high-temperature hexagonal structure ($a = 4.925$ Å, $c = 8.062$ Å, $c/a = 1.637$). Elliott considers the compound isomorphous with MgZn₂ at all temperatures from 600 to 1200 C.⁽¹²⁴⁾ Grigor'ev et al.⁽²³³⁾ states that TaCr₂ undergoes a polymorphic transformation at 1805 C. They report that the solubility of chromium in tantalum is about 5 weight per cent at 1800 C, and the solubility of tantalum in chromium is about 10 weight per cent at 1700 C. Grigor'ev,⁽³⁰⁰⁾ et al., reported five structural modifications in the chromium-rich region. The ϵ solid solution has a body-centered cubic lattice whose parameters can be extrapolated to α -chromium. Alloys in the region of the γ solid solution have a similar lattice. Alloys with 5 weight per cent tantalum quenched from 1550 C contained body-centered cubic ϵ and a second phase δ which has a hexagonal lattice with $a = 2.841$ kX, $c = 4.786$ kX, and $c/a = 1.685$.

TANTALUM-COBALT SYSTEM

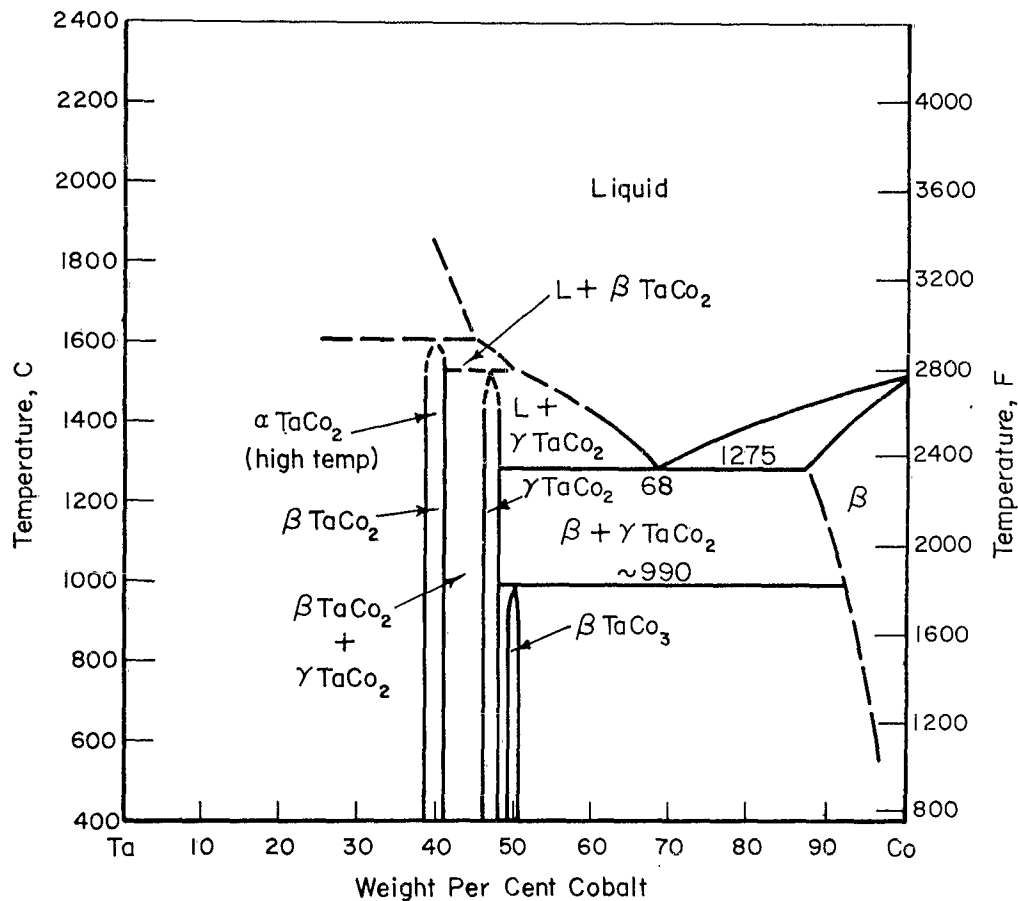


Two Laves phases were identified in a 39.4 weight per cent cobalt alloy.⁽³⁰⁵⁾ α -TaCo₂, a hexagonal MgZn₂-type structure with $a = 4.797$ Å, $c = 7.827$ Å, and $c/a = 1.632$ was present in the as-cast microstructure. Aging at 1100 and 1200 C transformed α -TaCo₂ to a cubic MgCu₂-type phase β -TaCo₂ with $a = 6.778$. Elliot also observed both structures.⁽¹²⁴⁾ γ -TaCo₂ is also a Laves phase of the hexagonal MgNi₂ type with $a = 4.700$ Å, $c = 15.42$ Å, and $c/a = 3.281$.^(120, 305) β -TaCo₃ is hexagonal with $a = 9.411$ Å, $c = 15.50$ Å, and $c/a = 1.647$.⁽³⁰⁵⁾ A metastable ordered cubic phase ($a = 3.647$ Å) of the AuCu₃ type was also reported.⁽³⁰⁵⁾ Contributions to the above diagram were made by Köster and Mulfinger⁽¹²¹⁾ and by Hoschimoto⁽¹²²⁾.

TANTALUM-GOLD SYSTEM

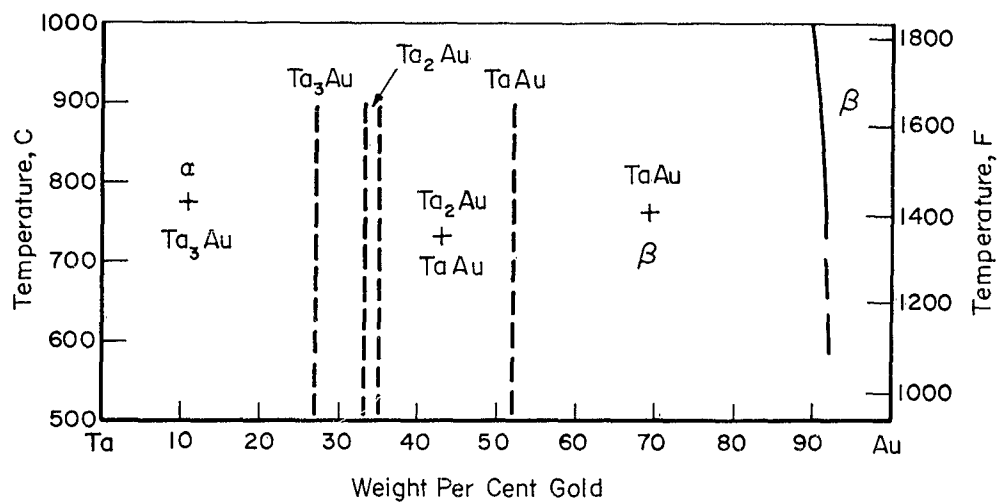


Ta_3Au has a cubic Cr_3O -type structure with $a = 5.21$ kX. Ta_2Au is a tetragonal σ -type phase with $a = 10.04$ kX and $c/a = 0.520$. $TaAu$ has a tetragonal structure with $a = 3.37$ kX and $c/a = 0.902$. The solubility of tantalum in gold is 10 weight per cent at 1000 C, decreasing to 8.7 weight per cent at 800 C. (252)

TANTALUM-IRIDIUM SYSTEM

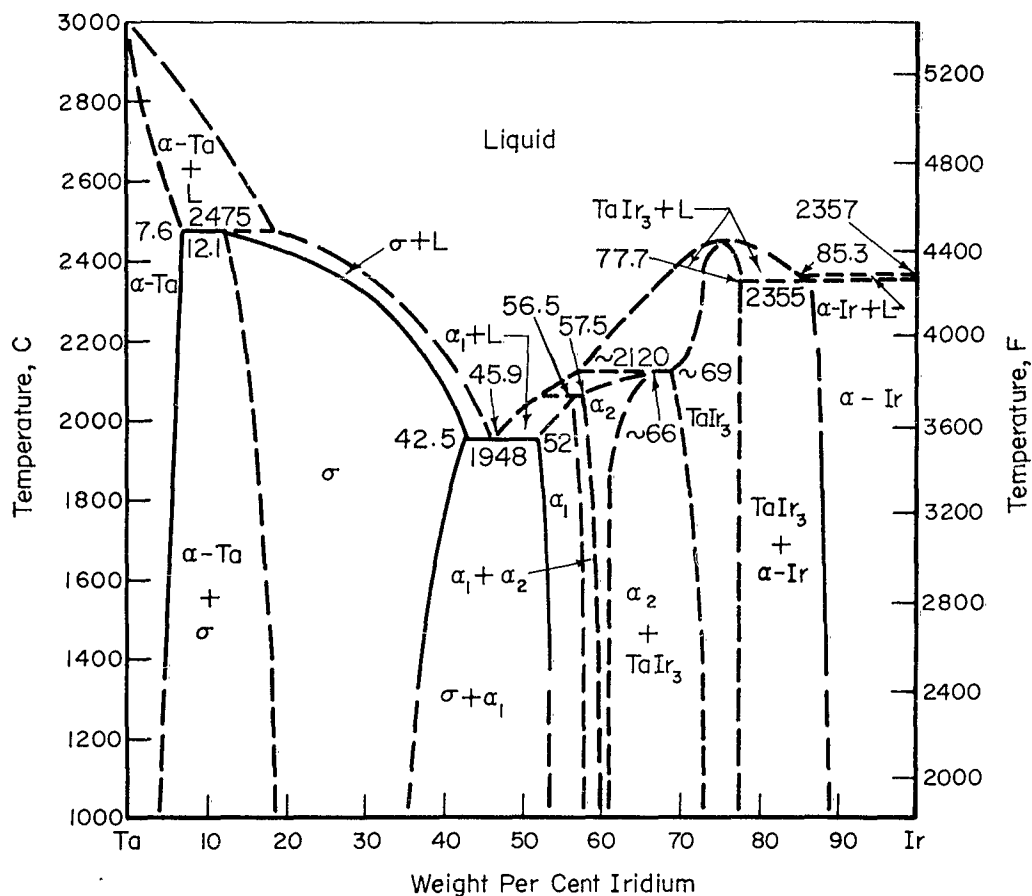


Sigma has a tetragonal $\sigma(\text{FeCr})$ structure with $a = 9.938 \text{ \AA}$ and $c = 5.172 \text{ \AA}$ at 25 atomic per cent (26 weight per cent) iridium.⁽²⁵³⁾ α_1 has a structure similar to the α_1 phase in the tantalum-rhodium system.⁽²⁵⁴⁾ α_2 has a tetragonal AuCu structure with $a = 3.991 \text{ \AA}$, $c = 3.856 \text{ \AA}$, and $c/a = 0.966$.⁽²⁵⁴⁾ The structure of TaIr_3 is a cubic, AuCu_3 type with $a = 3.889 \text{ \AA}$.⁽²⁵⁵⁾ α -tantalum has a maximum solubility of 7.2 atomic per cent (7.6 weight per cent) iridium at 2475°C.⁽²⁵⁴⁾

TANTALUM-MANGANESE SYSTEM

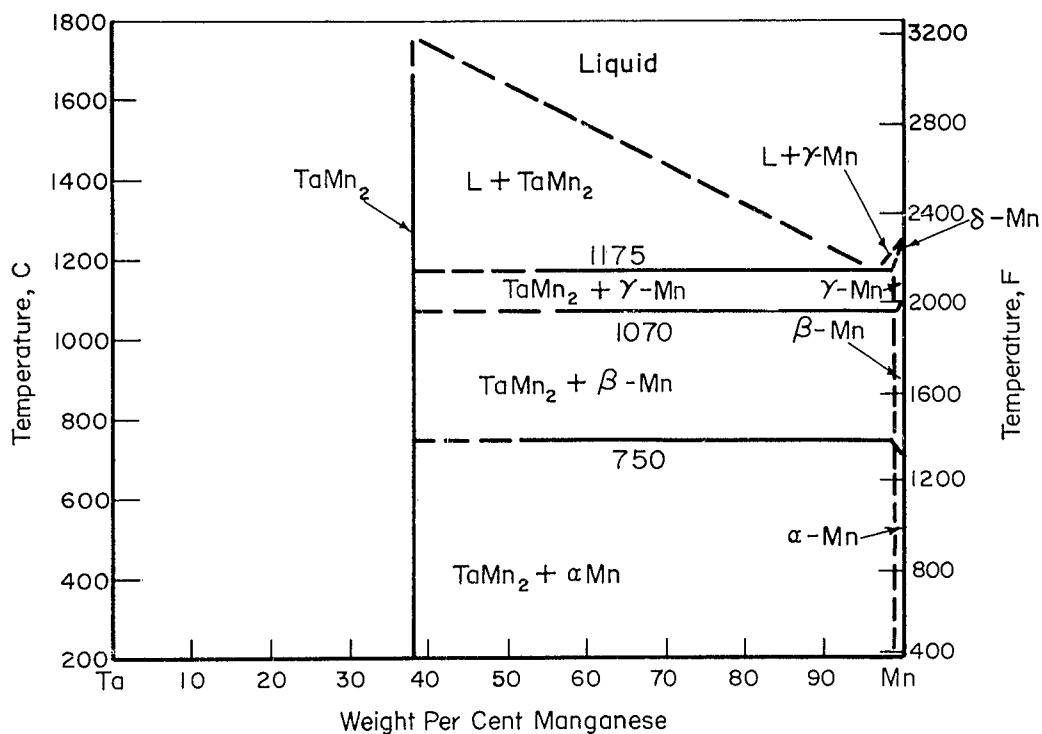


TaMn₂ has a hexagonal MgZn₂ Laves-phase-type structure with $a = 4.864 \text{ \AA}$, $c = 7.947 \text{ \AA}$, and $c/a = 1.634$.⁽¹²⁴⁾ This compound has a melting point above 1670°C.⁽²⁹⁸⁾ At 1070°C, the $\beta \rightleftharpoons \gamma$ transition occurs by a eutectoid reaction. The δ -manganese $\rightleftharpoons \gamma$ -manganese transformation is a peritectic reaction and occurs near the melting point.⁽²⁹⁸⁾

TANTALUM-NITROGEN SYSTEM

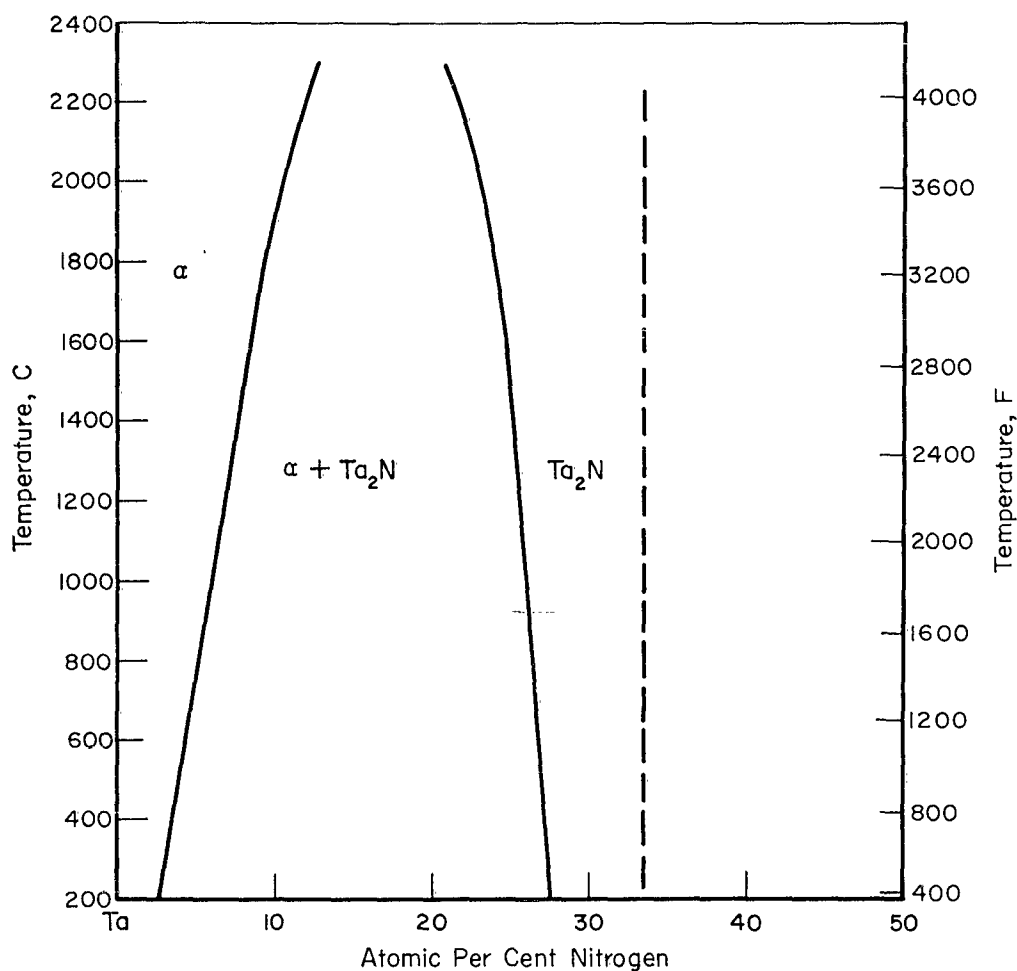


Two intermetallic compounds are definitely established for the tantalum-nitrogen system. TaN is close-packed hexagonal with $a = 5.181$ kX, $c = 2.905$ kX, and $c/a = 0.561$.⁽¹³²⁾ Ta_2N is also close-packed hexagonal with $a = 3.042$ kX, $c = 4.909$ kX, and $c/a = 1.614$.^(132, 133) The melting point of TaN has been given as 2890 C⁽¹³⁴⁾ and 3090 C⁽¹³⁵⁾. Chiotti has shown that TaN dissociates at high temperatures, forming the lower nitride, Ta_2N , and nitrogen.⁽¹³⁶⁾ The phase diagram was obtained from Reference (256).

TANTALUM-PLATINUM SYSTEM

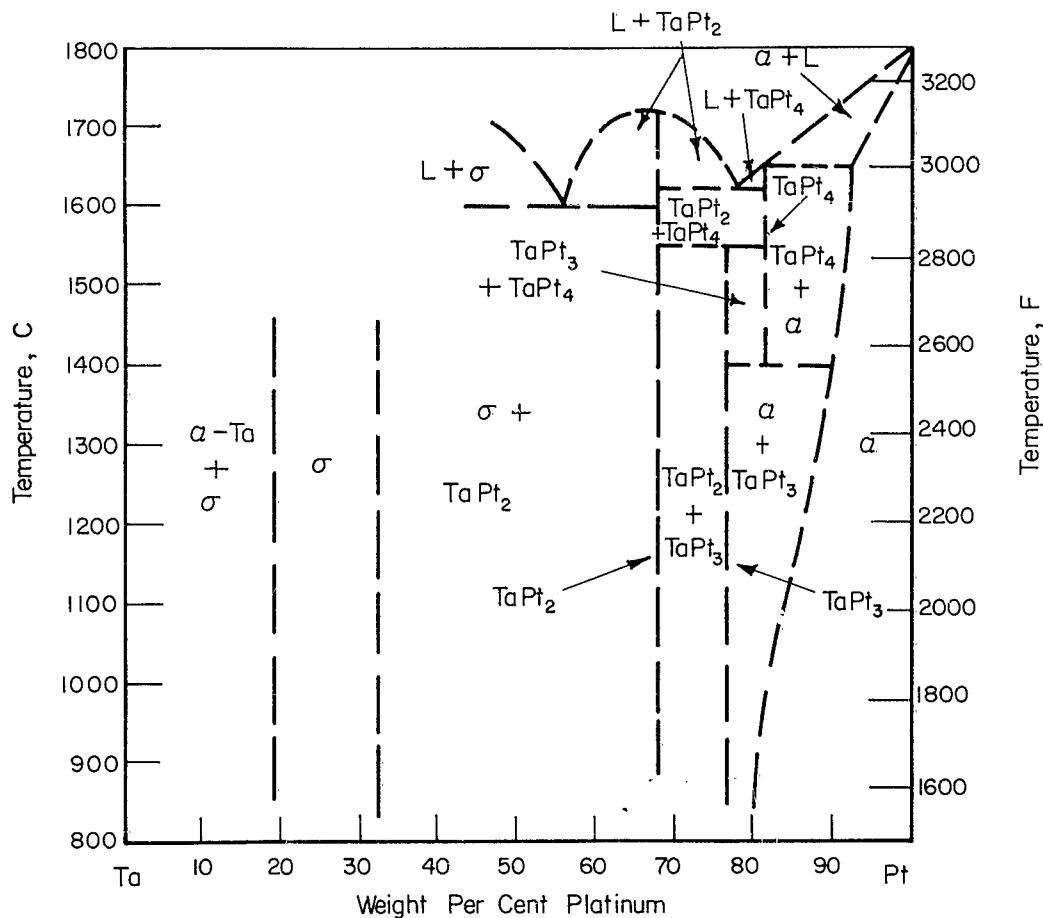


Four intermediate phases were observed between 50 and 100 per cent platinum. The σ -phase has a complex tetragonal structure with 30 atoms per unit cell;⁽²⁵⁷⁾ cell dimensions are $a = 9.95 \text{ \AA}$, $c = 5.16 \text{ \AA}$, and $c/a = 0.52$.⁽³⁰⁾ TaPt_4 is stable above 1000 C and has a tetragonal structure with $a = 8.58 \text{ \AA}$, $c = 10.60 \text{ \AA}$, and $c/a = 1.24$. TaPt_3 is tetragonal with $a = 6.45 \text{ \AA}$, $c = 6.98 \text{ \AA}$, and $c/a = 1.08$. The TaPt_2 phase was not clearly established by the X-ray results. The solubility of tantalum in platinum is about 10 atomic per cent (9 weight per cent) at 1500 C and 20 atomic per cent (19 weight per cent) at 1000 C. The exact phase boundaries and reaction isotherms were not determined in this investigation by Browning.⁽²⁵⁷⁾

TANTALUM-RHODIUM SYSTEM

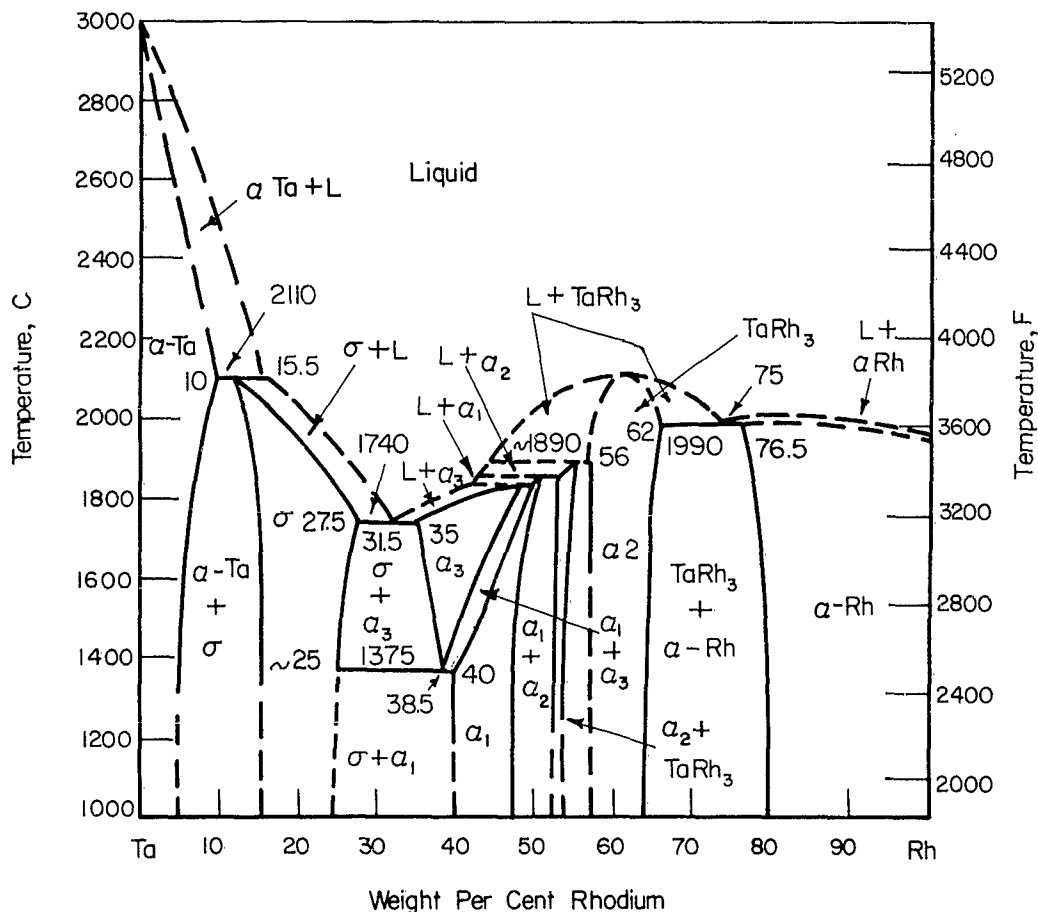


Five intermediate phases occur in the system. Sigma has a tetragonal $\sigma(\text{FeCr})$ type structure with $a = 9.754 \text{ \AA}$, $c = 5.058 \text{ \AA}$, and $c/a = 0.518$ at the rhodium-rich side.⁽⁹¹⁾ α_1 is orthorhombic, similar to VCo_3 , with $a = 5.62 \text{ \AA}$, $b = 9.48 \text{ \AA}$, and $c = 13.61 \text{ \AA}$.⁽²⁵⁴⁾ α_2 is orthorhombic and probably isomorphous with Co_2Si with $a = 5.45 \text{ \AA}$, $b = 8.15 \text{ \AA}$, and $c = 4.01 \text{ \AA}$.⁽²⁵⁴⁾ The structure of α_3 is unknown.⁽²⁵⁴⁾ TaRh_3 has a cubic AuCu_3 -type structure with $a = 3.86 \text{ \AA}$.⁽²⁵⁵⁾ The maximum solubility of rhodium in tantalum is 16 ± 1 atomic per cent (10 weight per cent) at 2110 C; tantalum is soluble in rhodium up to 15 ± 0.5 atomic per cent (23.5 weight per cent) at 1990 C.⁽²⁵⁴⁾

TANTALUM-THORIUM SYSTEM

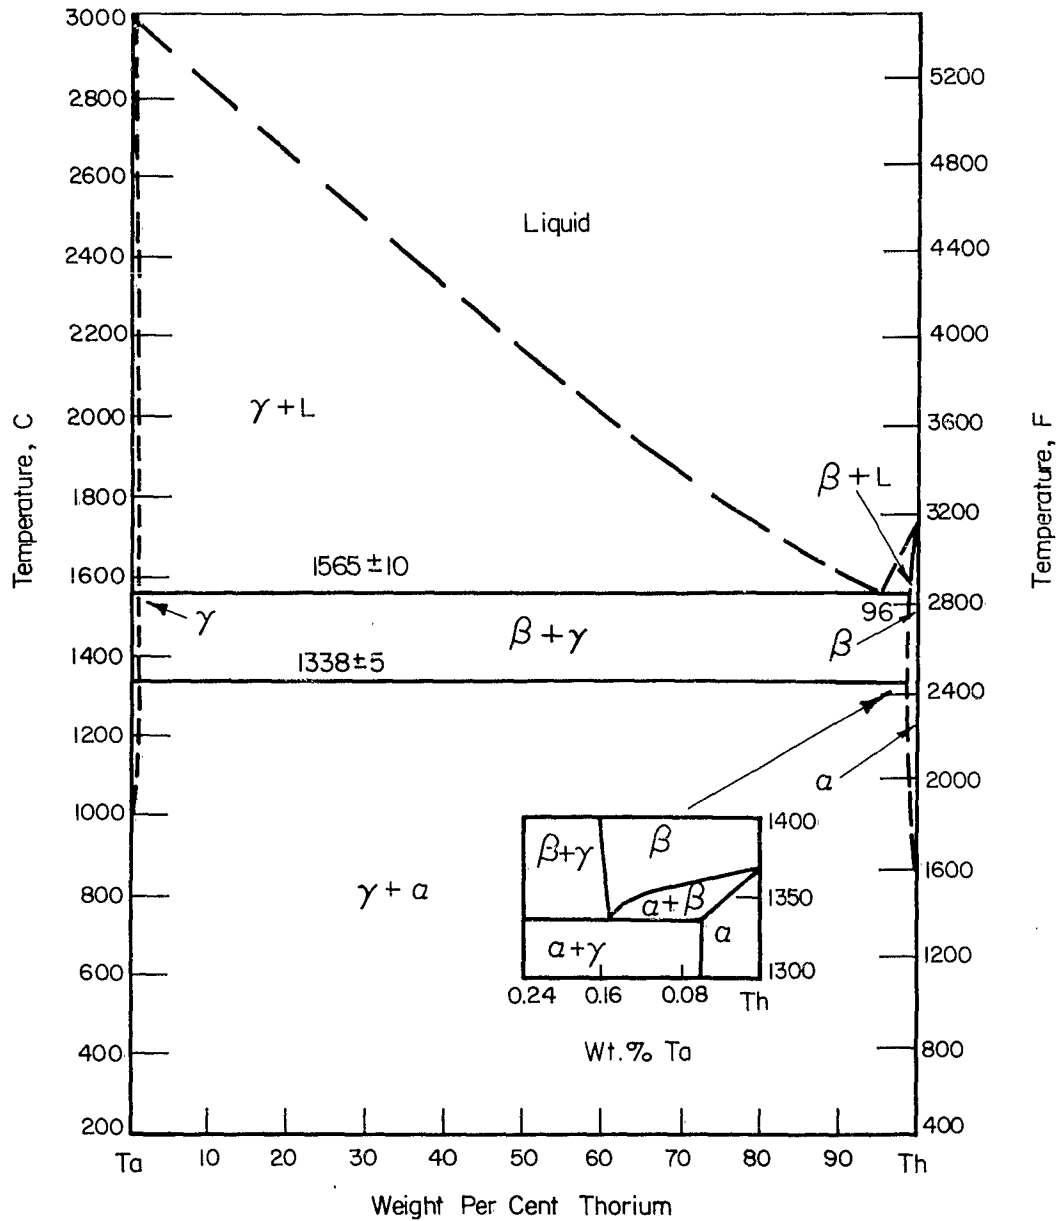


The solubility of thorium in tantalum is less than 0.2 weight per cent at the eutectic temperature. The solubility of tantalum in thorium at the eutectic temperature is about 0.4 weight per cent, and below 1340 C, is less than 0.2 weight per cent. No evidence of intermediate phases was found.⁽³⁰⁶⁾

TANTALUM-YTTRIUM SYSTEM

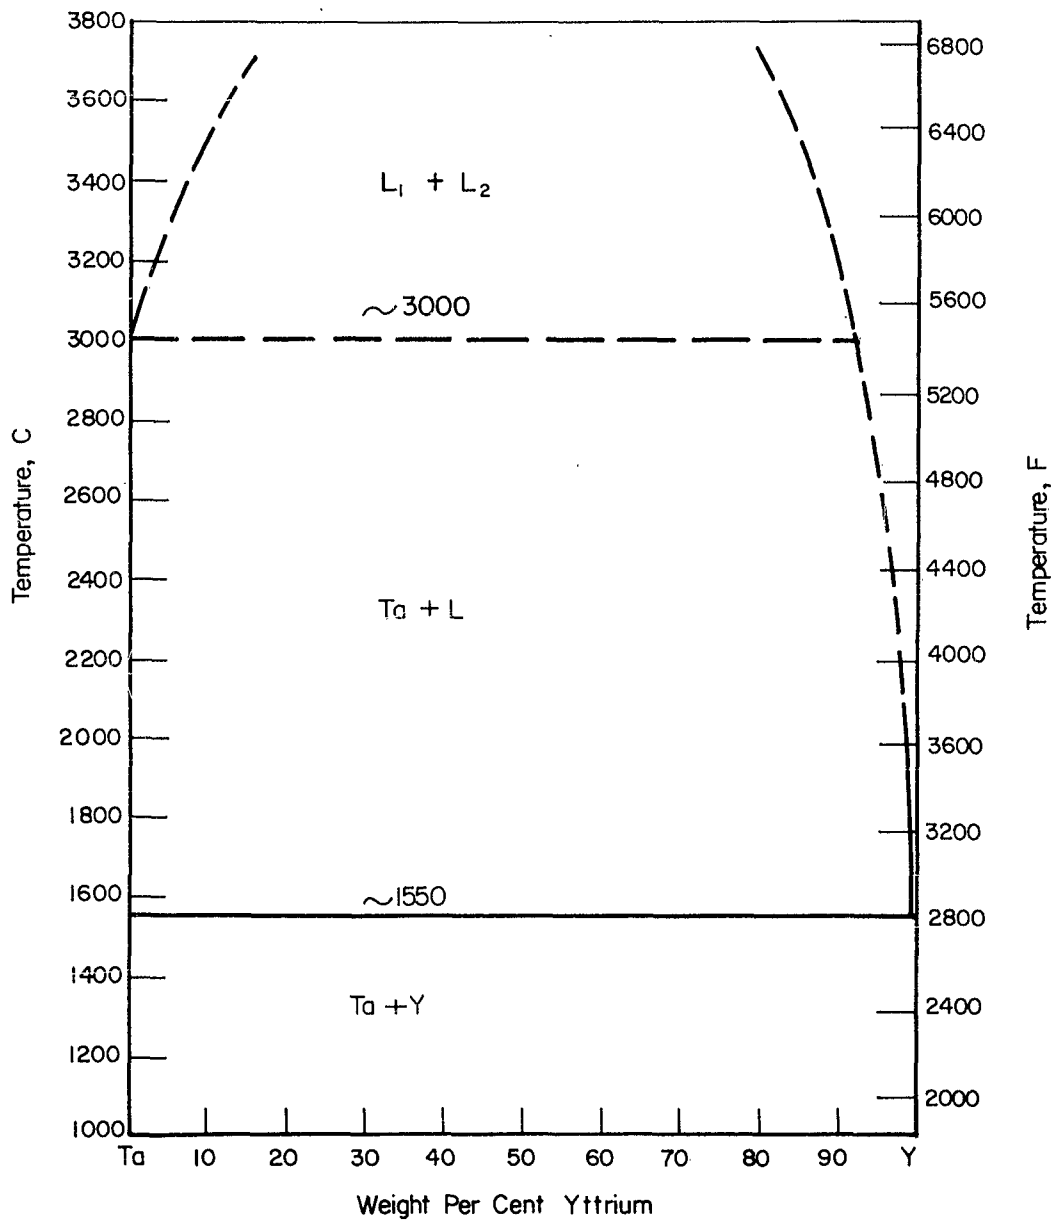


Terminal solubilities are about 0.1 weight per cent. (248, 249)

TANTALUM-ZIRCONIUM SYSTEM

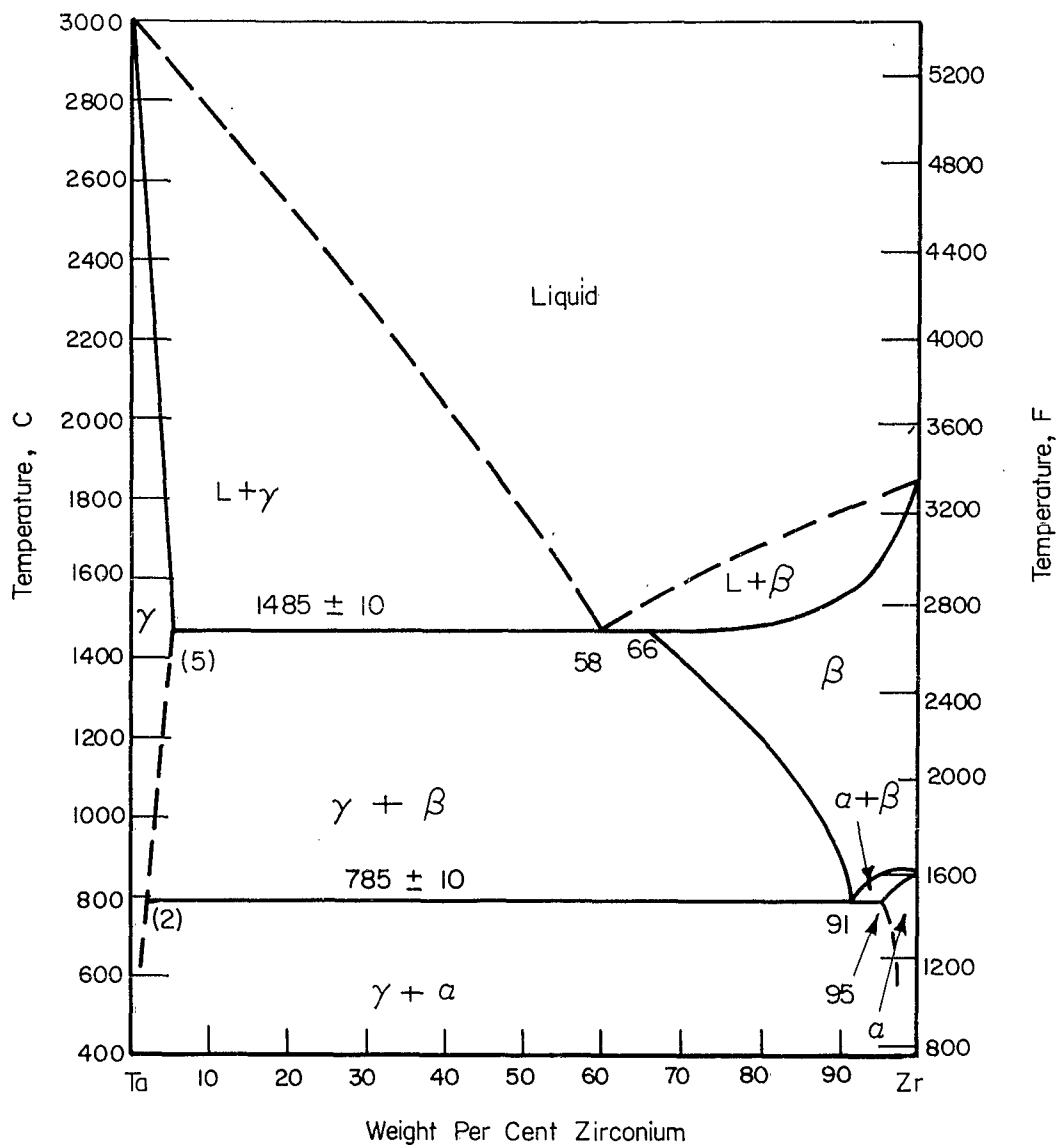


Pease, et al.,⁽²⁵⁸⁾ locate the eutectic temperature at 1485 C with the eutectic composition at 58 weight per cent (73 atomic per cent) zirconium. The eutectoid composition was given as 91 weight per cent (95.5 $\pm$ 1 atomic per cent) zirconium at 785 $\pm$ 10 C, the temperature agreeing with Emilyanov, et al.⁽¹⁶⁰⁾ Possible oxygen contamination could have affected Pease's results.

TUNGSTEN-BORON SYSTEM

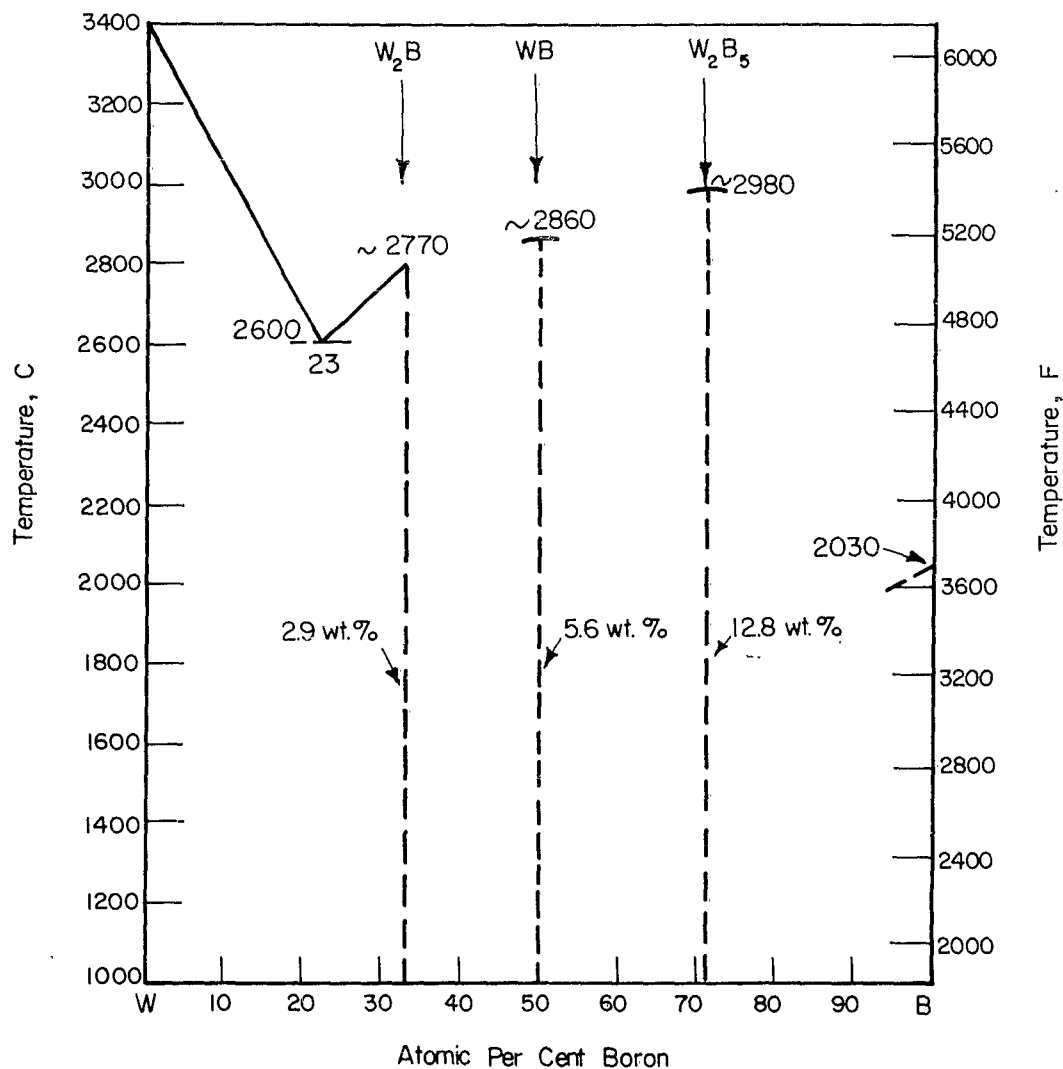


W₂B is tetragonal of the CuAl₂ (C16) type with $a = 5.564 \text{ \AA}$, $c = 4.740 \text{ \AA}$, and $c/a = 0.852$.⁽⁵⁸⁾ A low-temperature form of WB, stable below 1850 C, is tetragonal (MoB type) with $a = 3.115 \text{ \AA}$, $c = 16.93 \text{ \AA}$, and $c/a = 5.44$.⁽⁵⁸⁾ The high-temperature modification, corresponding to β -MoB, is orthorhombic (CrB type) with $a = 3.19 \text{ \AA}$, $b = 8.40 \text{ \AA}$, $c = 3.07 \text{ \AA}$.⁽¹⁶⁴⁾ W₂B₅ has a hexagonal defect structure with $a = 2.982 \text{ \AA}$, $c = 13.87 \text{ \AA}$, and $c/a = 4.65$.⁽¹⁶⁴⁾ The W-W₂B eutectic temperature is 2600 C at 23 atomic per cent boron.⁽²⁵⁹⁾

TUNGSTEN-CARBON SYSTEM

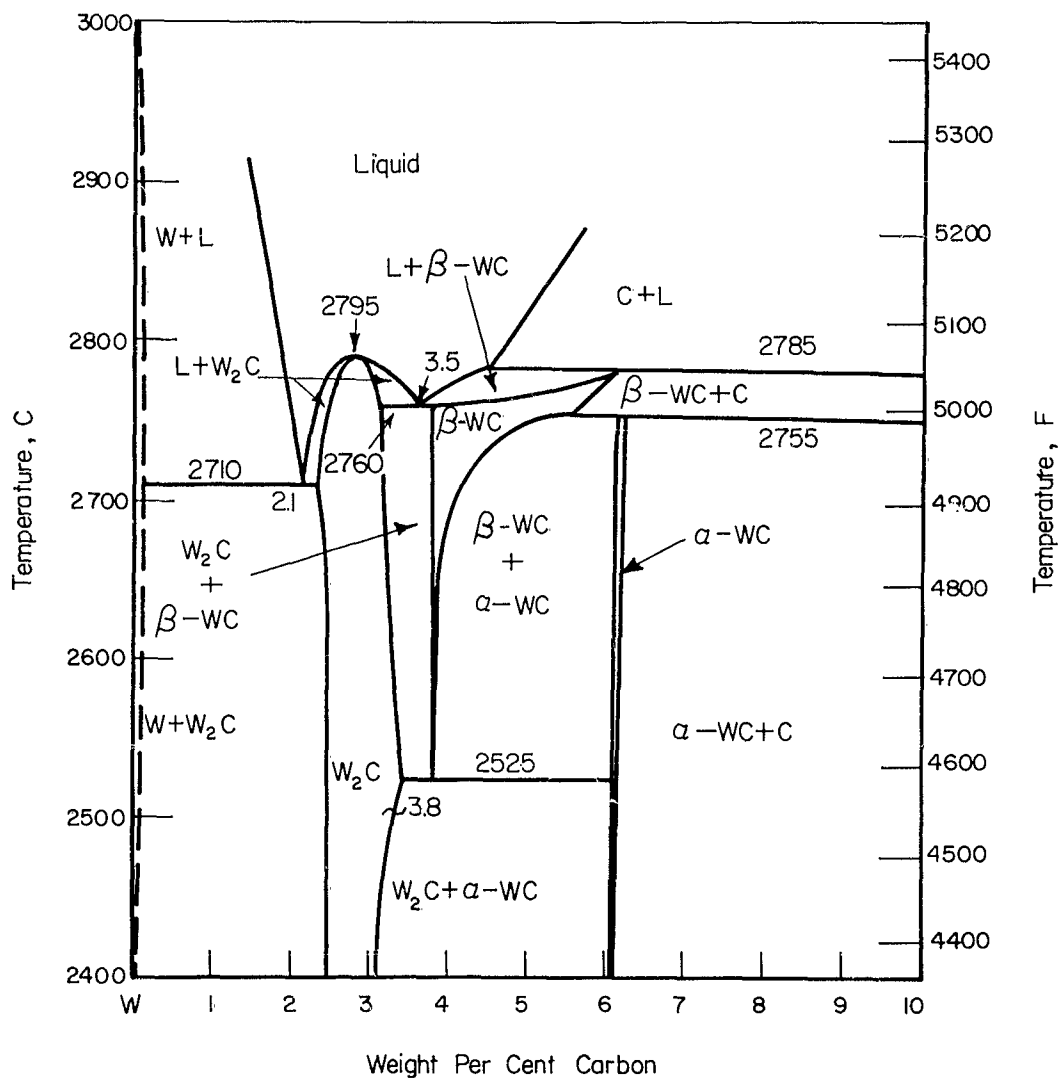


Three intermediate phases were identified by Dolloff, W_2C , α -WC, and β -WC.⁽²⁶⁰⁾ Only one crystal modification of W_2C was found by Dolloff in contrast to Becker's⁽¹⁶⁵⁾ and Goldschmidt's⁽²⁵⁹⁾ results of two structures -- the low-temperature modification being hexagonal with $a = 2.994$ Å, $c = 4.724$ Å, and $c/a = 1.578$, and the high-temperature W_2C modification having a face-centered cubic structure with $a = 4.16$ Å. A newly reported phase, β -WC, has a face-centered cubic structure with $a = 4.125$ Å for the composition $WC_{0.82}$.⁽²⁶⁰⁾ Hexagonal α -WC is essentially a line compound with $a = 2.906$ Å, $c = 2.837$ Å, and $c/a = 0.976$.⁽¹⁶⁵⁾ Goldsmith reported the solubility of carbon in tungsten as 0.30 atomic per cent near 2400 °C, decreasing to 0.05 atomic per cent near 2000 °C and to insignificant amounts at lower temperatures.⁽²⁵⁹⁾

TUNGSTEN-IRIDIUM SYSTEM

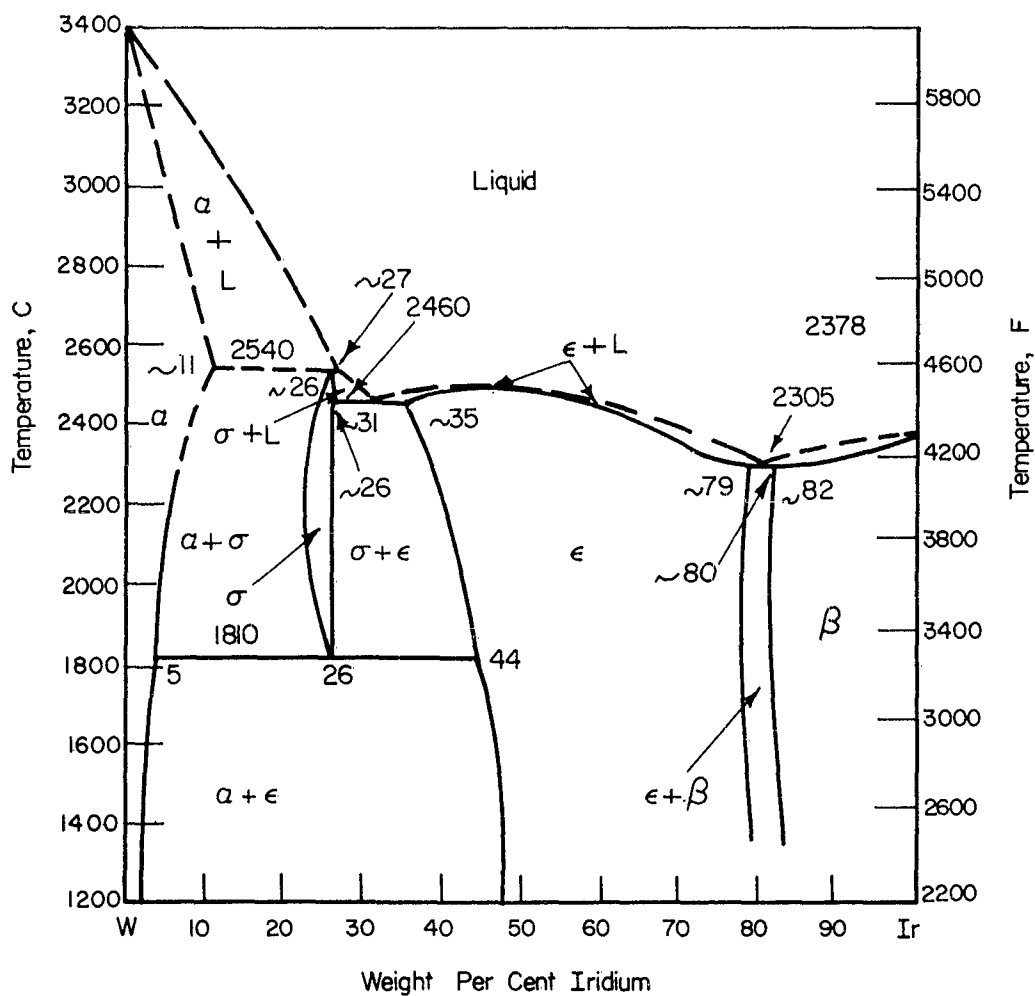


ϵ has been identified as a close-packed-hexagonal structure with $a = 2.736 \text{ \AA}$ and $c/a = 1.602$ at the iridium side and $a = 2.764 \text{ \AA}$ and $c/a = 1.611$ at the tungsten side of the homogeneity range.⁽²⁶¹⁾ The solubility of iridium in tungsten is about 11 weight per cent (~10 atomic per cent) at 2540 C, decreasing to about 5 weight per cent (~4 atomic per cent) at 1810 C. Tungsten is soluble in iridium up to 18 weight per cent (~19 atomic per cent) at 2305 C.⁽²⁶²⁾

TUNGSTEN-LEAD SYSTEM

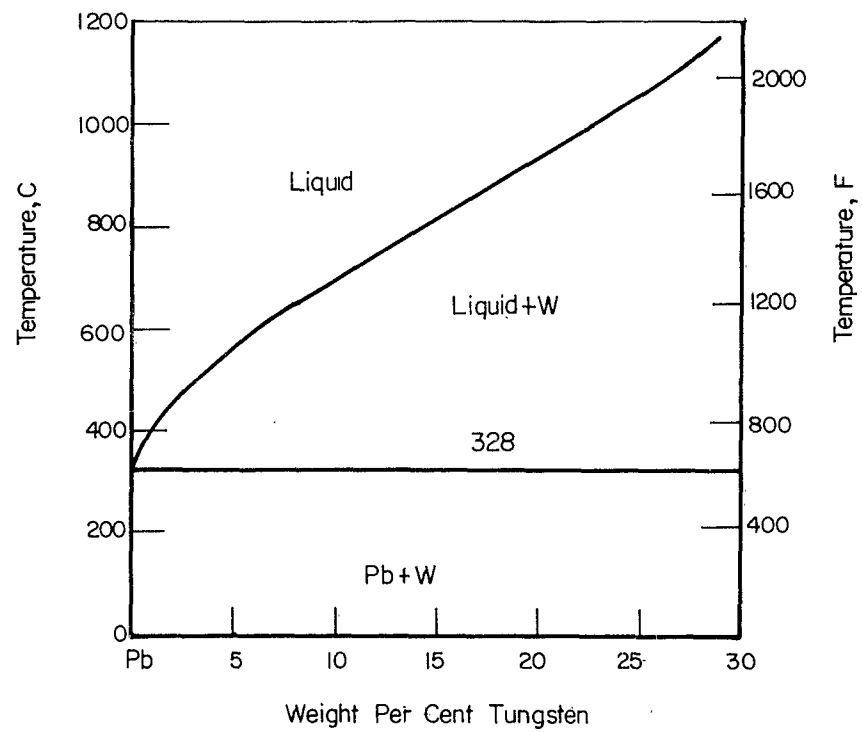


No intermetallic compounds exist in the system. (263)

TUNGSTEN-OXYGEN SYSTEM

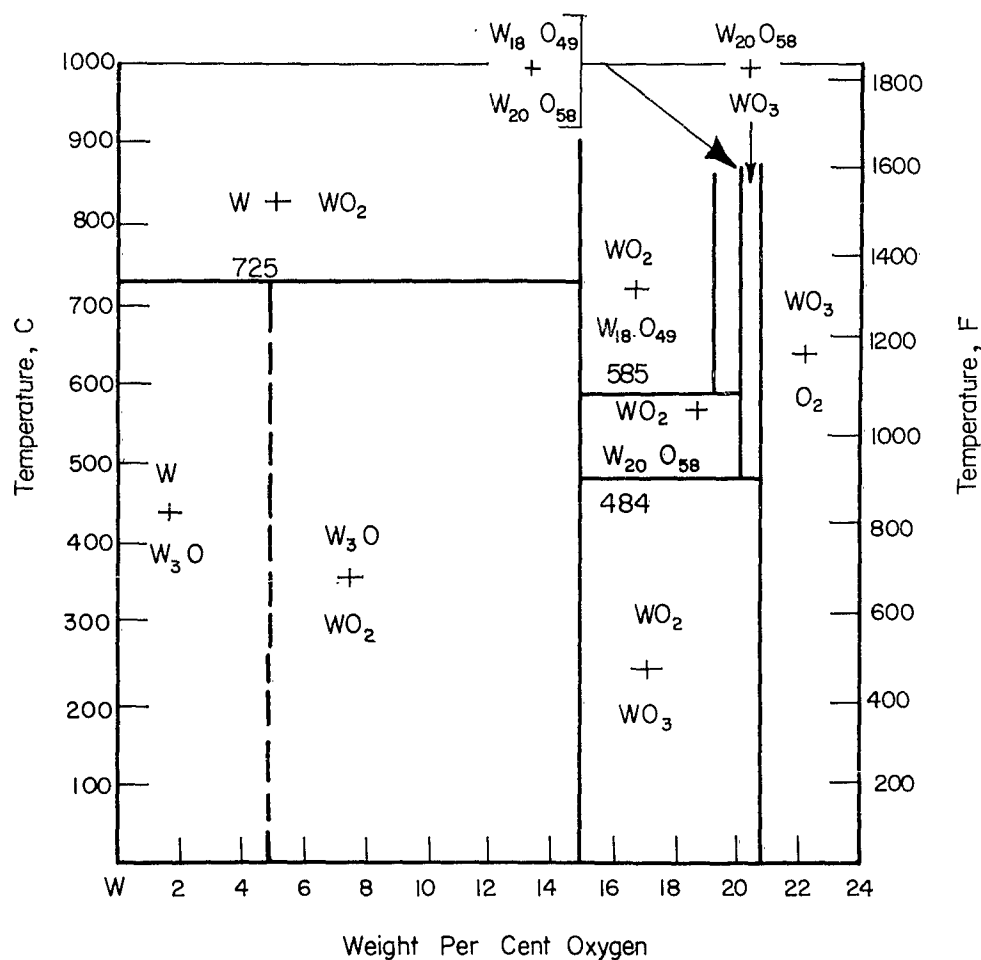


WO₂ has a monoclinic structure isomorphous with MoO₂, with $a = 5.560 \text{ \AA}$, $b = 4.884 \text{ \AA}$, $c = 5.546 \text{ \AA}$, $\beta = 118.93^\circ$, and 12 atoms per unit cell.⁽¹⁹⁹⁾ W₁₈O₄₉ has a monoclinic structure with $a = 18.32 \text{ \AA}$, $b = 3.79 \text{ \AA}$, $c = 11.04 \text{ \AA}$, $\beta = 115^\circ 2'$, and 67 atoms per unit cell.⁽²⁰⁰⁾ The structure of W₂₀O₅₈ is closely related to monoclinic ReO₃ (DO₉ type) with $a = 12.1 \text{ \AA}$, $b = 3.78 \text{ \AA}$, $c = 23.4 \text{ \AA}$, and $\beta = 95^\circ$.⁽²⁰⁰⁾ WO₃ is reported to have three structural modifications. The room temperature form is monoclinic with $a = 7.285 \text{ \AA}$, $b = 7.517 \text{ \AA}$, $c = 3.835 \text{ \AA}$, and $\beta = 90.90^\circ$.⁽²⁰¹⁾ At -50°C, a polymorphic transformation occurs, resulting in a structure of higher symmetry than the room-temperature modification.⁽²⁰²⁾ Between 700 and 750°C, a polymorphic transformation occurs, resulting in a tetragonal structure with $a = 5.25 \text{ \AA}$, $c = 3.92 \text{ \AA}$, $c/a = 0.746$, and 8 atoms per unit cell.⁽²⁰³⁾ The homogeneity ranges (oxygen/tungsten ratios) of the oxides at 1258°C are: WO₂ (1.99 to 2.02), W₁₈O₄₉ (2.66 to 2.77), and W₂₀O₅₈ (2.90 to 2.94).⁽²⁰⁰⁾ The diagram is from Reference (264).

TUNGSTEN-PALLADIUM SYSTEM

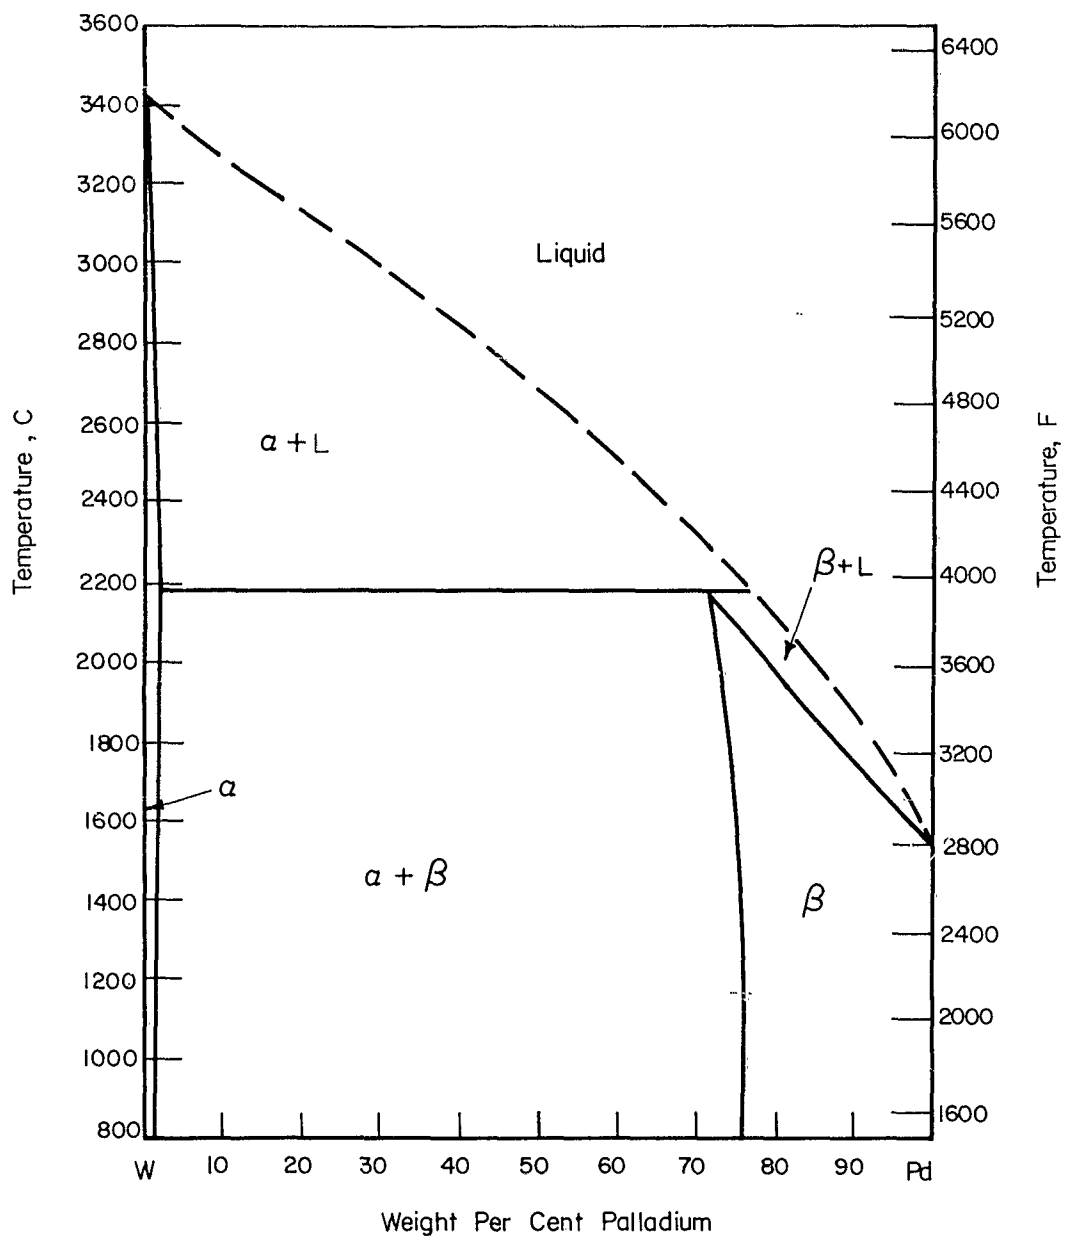


No intermediate phases are found in this system. The solubility of palladium in tungsten is 1.6 weight per cent at 1500 C. Tungsten dissolves in palladium up to 24 weight per cent at 1000 C. (265)

TUNGSTEN-RHODIUM SYSTEM

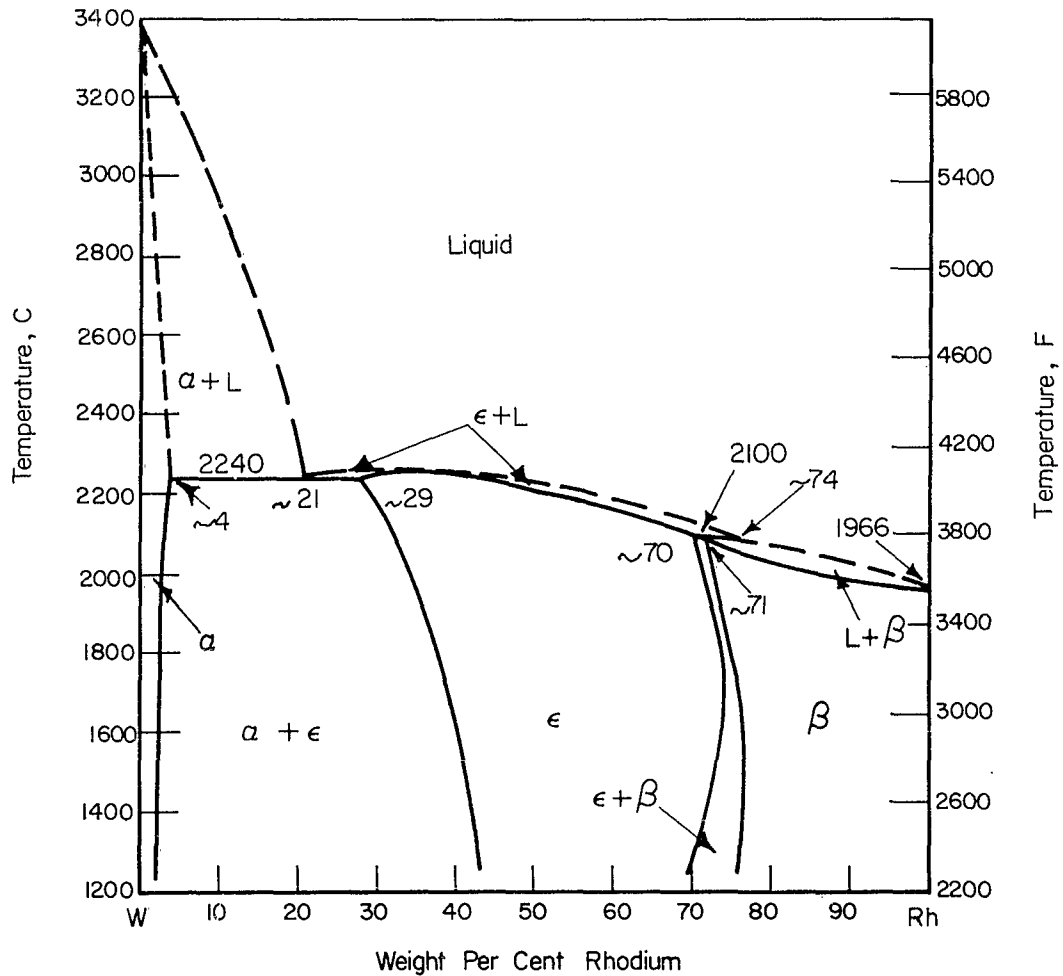

ε has a close-packed-hexagonal structure with $a = 2.708 \text{ \AA}$, $c = 4.328 \text{ \AA}$, and $c/a = 1.598$ at 70 weight per cent (80.8 atomic per cent) rhodium.⁽³⁰⁾ The solubility of rhodium in tungsten is about 4 weight per cent (6 atomic per cent) at 2240 C, decreasing to about 3 weight per cent (4 atomic per cent) at 1300 C. Tungsten is soluble in rhodium up to 29 weight per cent (19 atomic per cent) at 2100 C, decreasing to about 23 weight per cent (14 atomic per cent) at 1400 C.⁽²⁶²⁾


TUNGSTEN-YTTRIUM SYSTEM

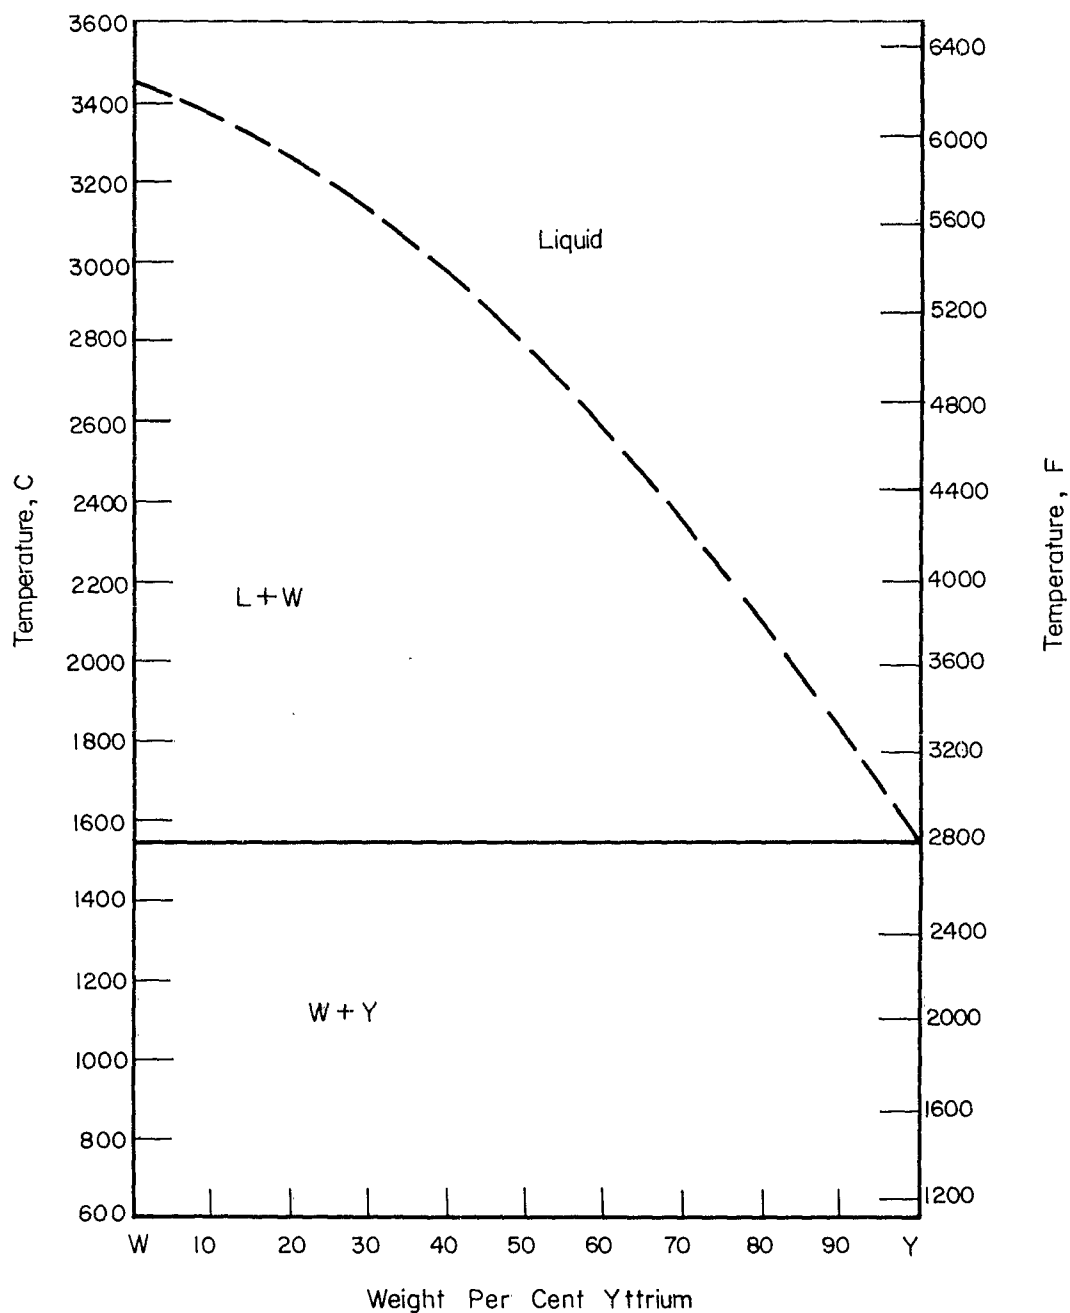


Terminal solubilities are probably less than 1 atomic per cent.⁽²⁴⁷⁾

TERNARY PHASE
DIAGRAMS


COLUMBIUM-ALUMINUM-NICKEL SYSTEM (Ni_3Al - Ni_3Cb SYSTEM) (317)

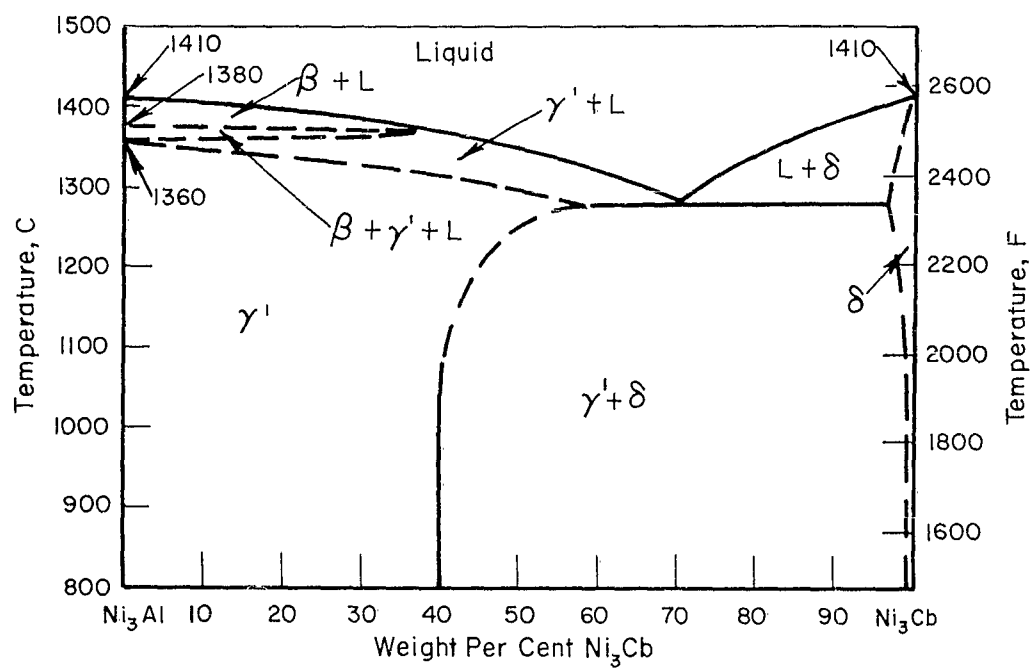


COLUMBIUM-ALUMINUM-SILICON SYSTEM (1400 C)(268)

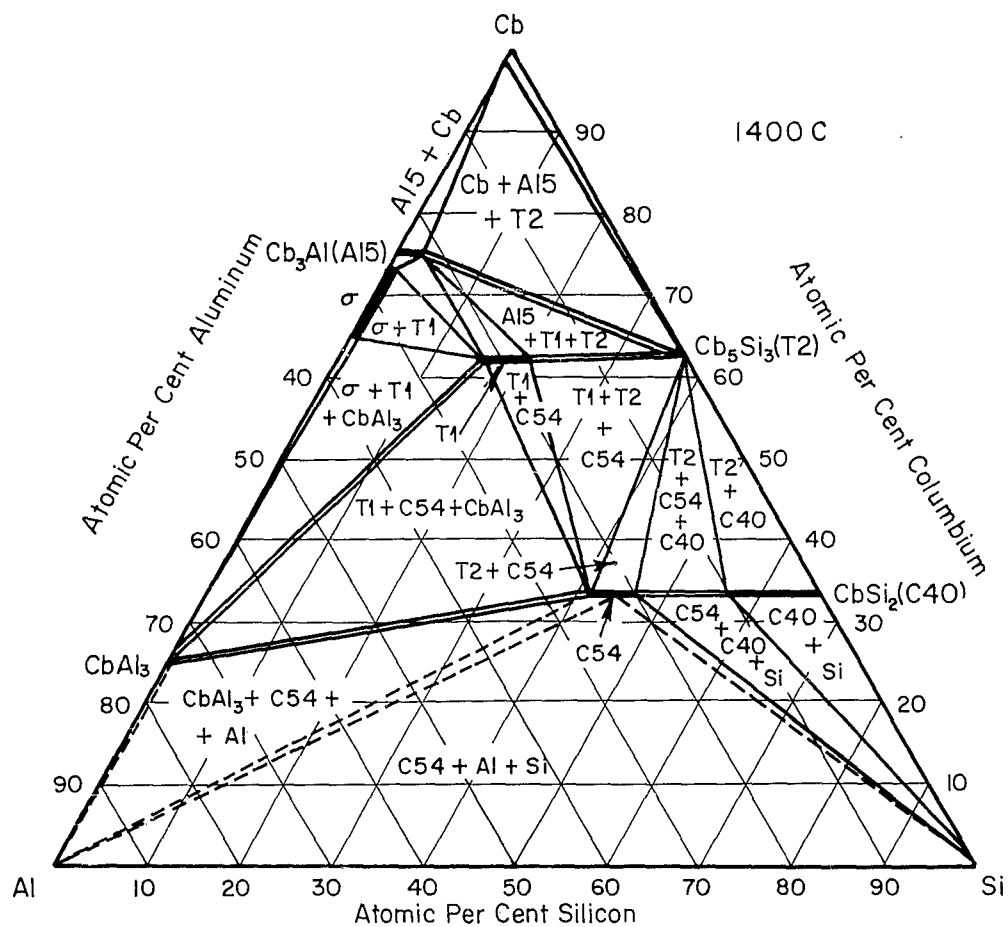


COLUMBIUM-ALUMINUM-TITANIUM SYSTEM (20 C)(269)

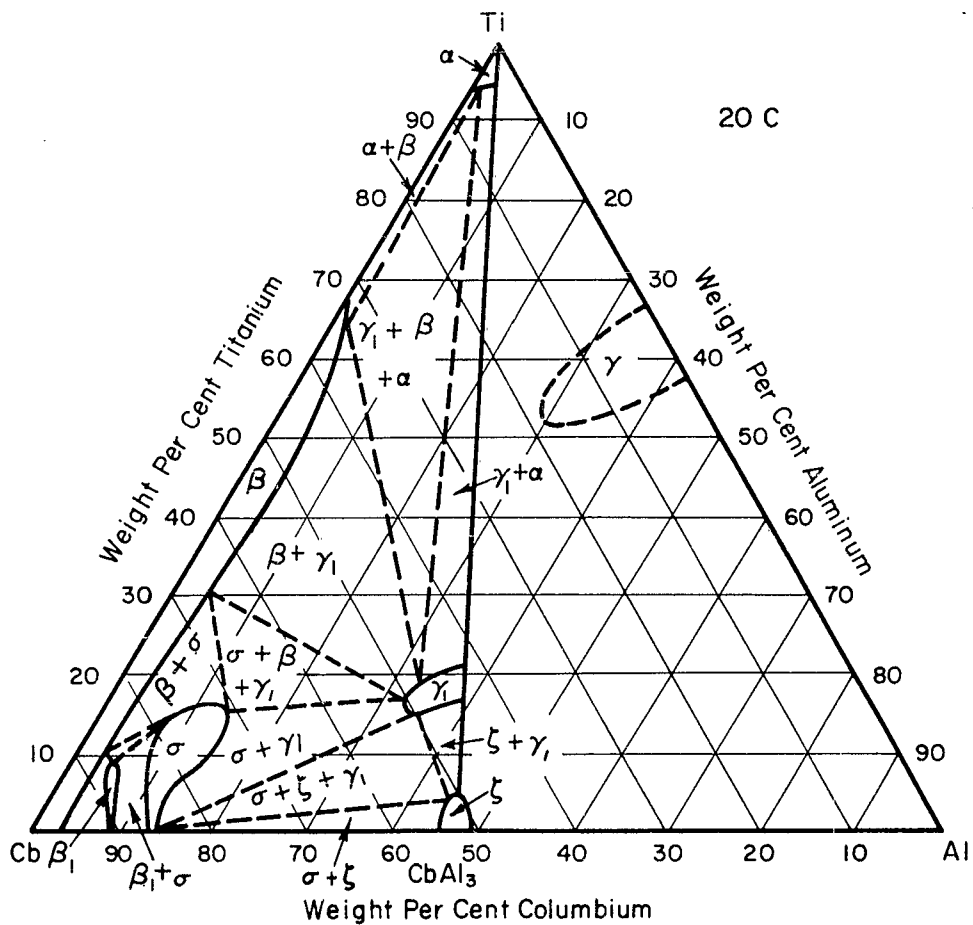


COLUMBIUM-ALUMINUM-TITANIUM SYSTEM (1200 C)(269)

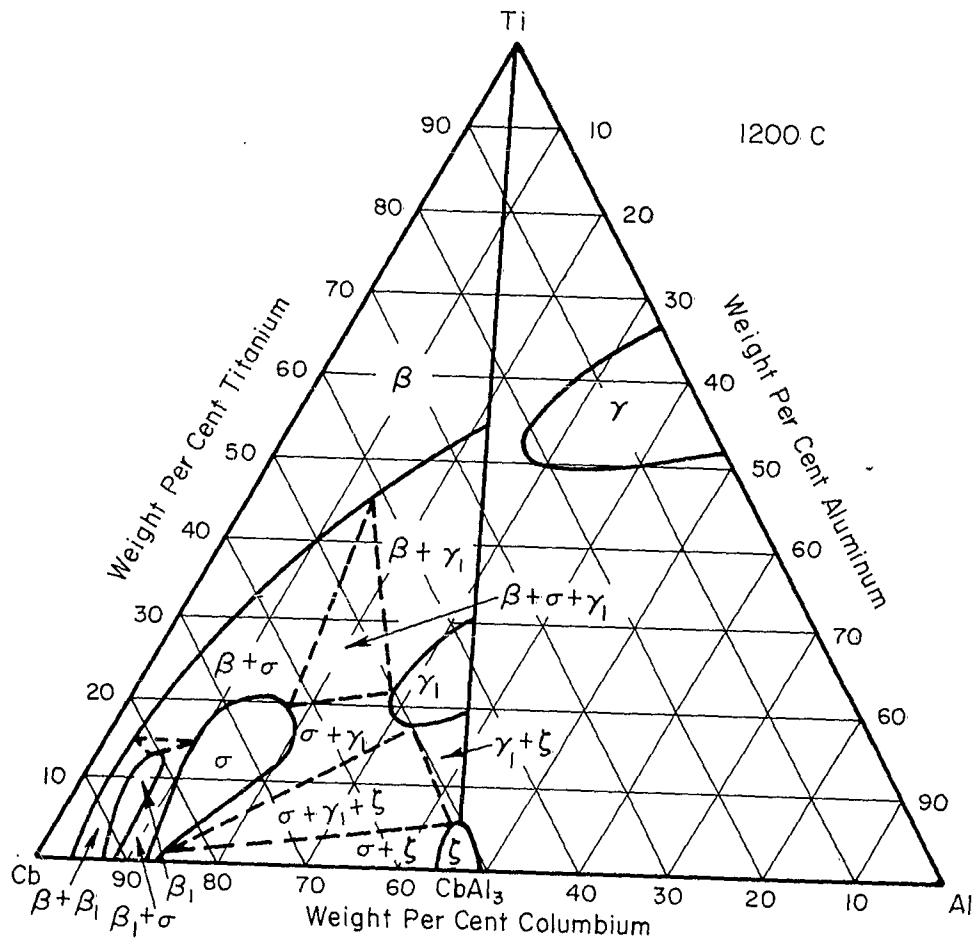


COLUMBIUM-BORON-SILICON SYSTEM (1600 C)(270)

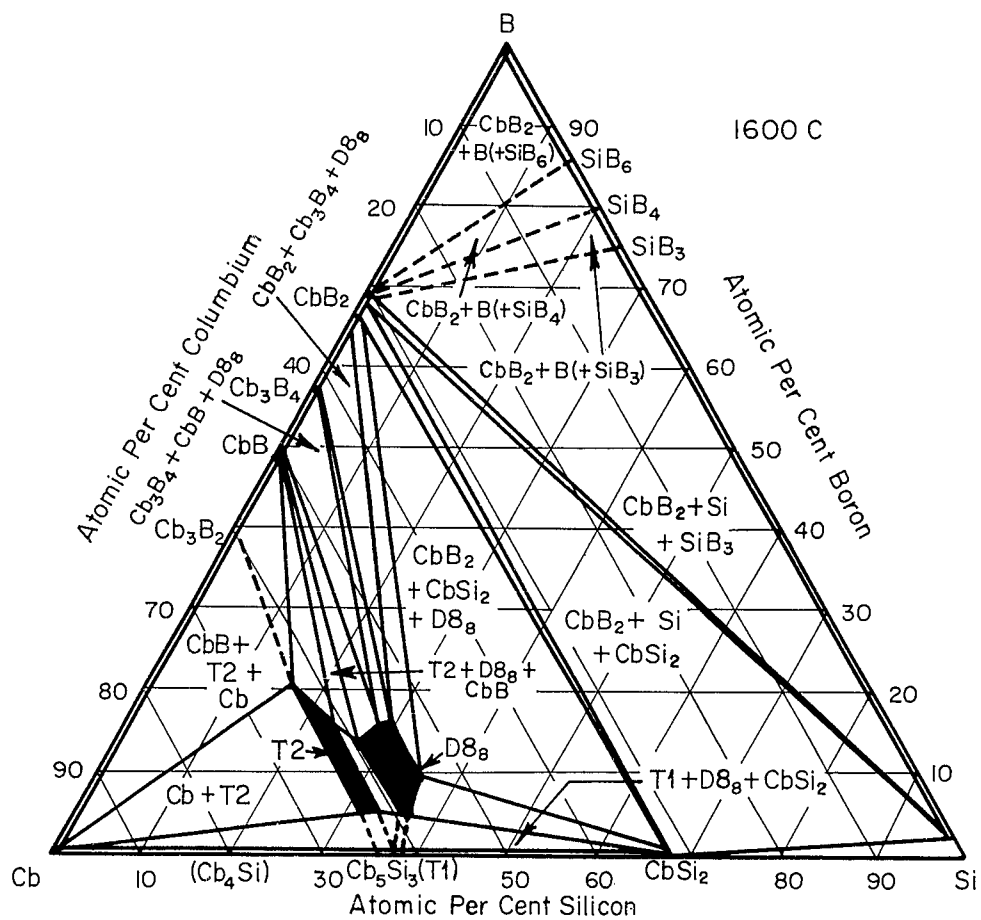


COLUMBIUM CARBIDE-HAFNIUM CARBIDE-URANIUM CARBIDE SYSTEM (2050 C)(271)

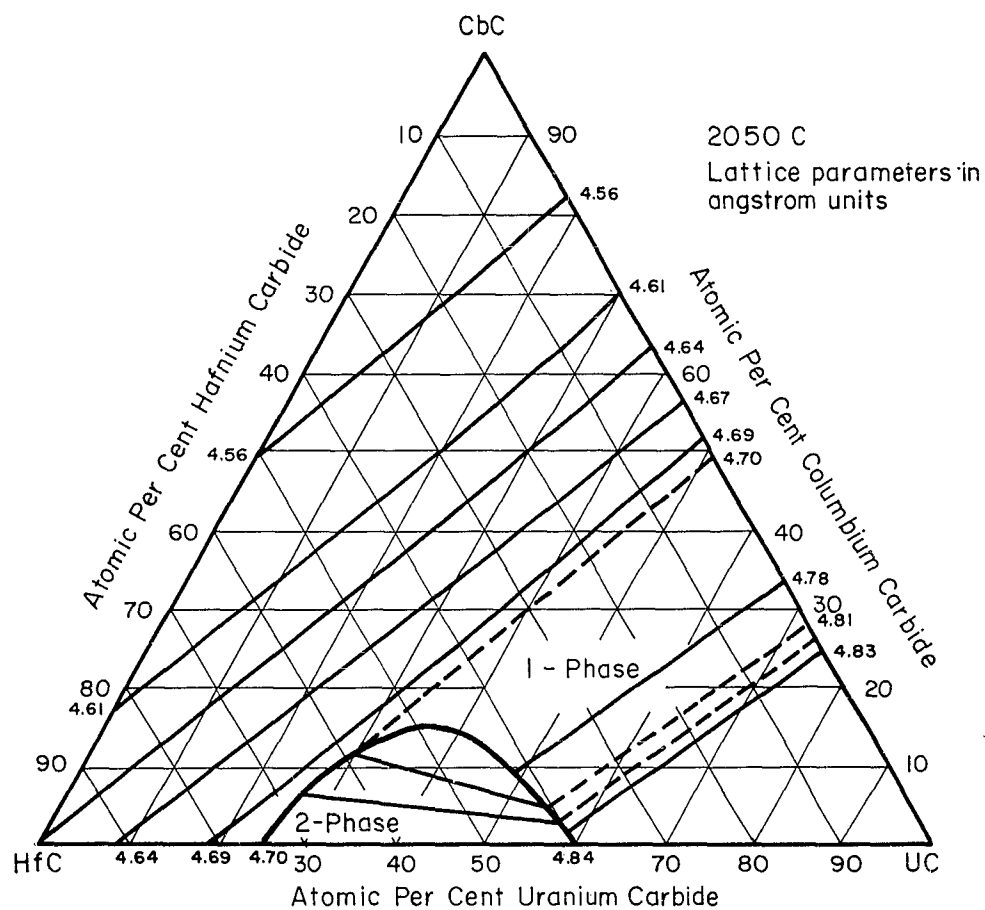


COLUMBIUM CARBIDE-HAFNIUM CARBIDE-VANADIUM CARBIDE SYSTEM (2050 C)⁽²⁷¹⁾

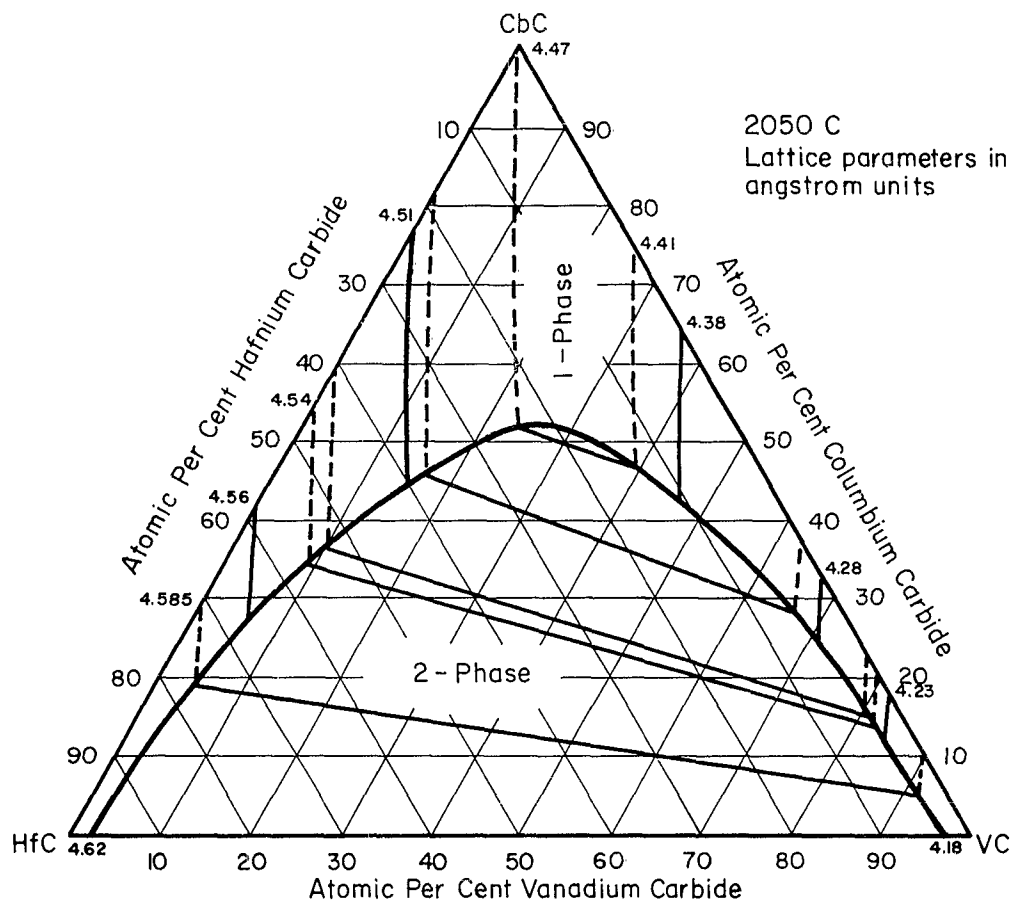

COLUMBIUM-CARBON-URANIUM SYSTEM (1700 C)(272)

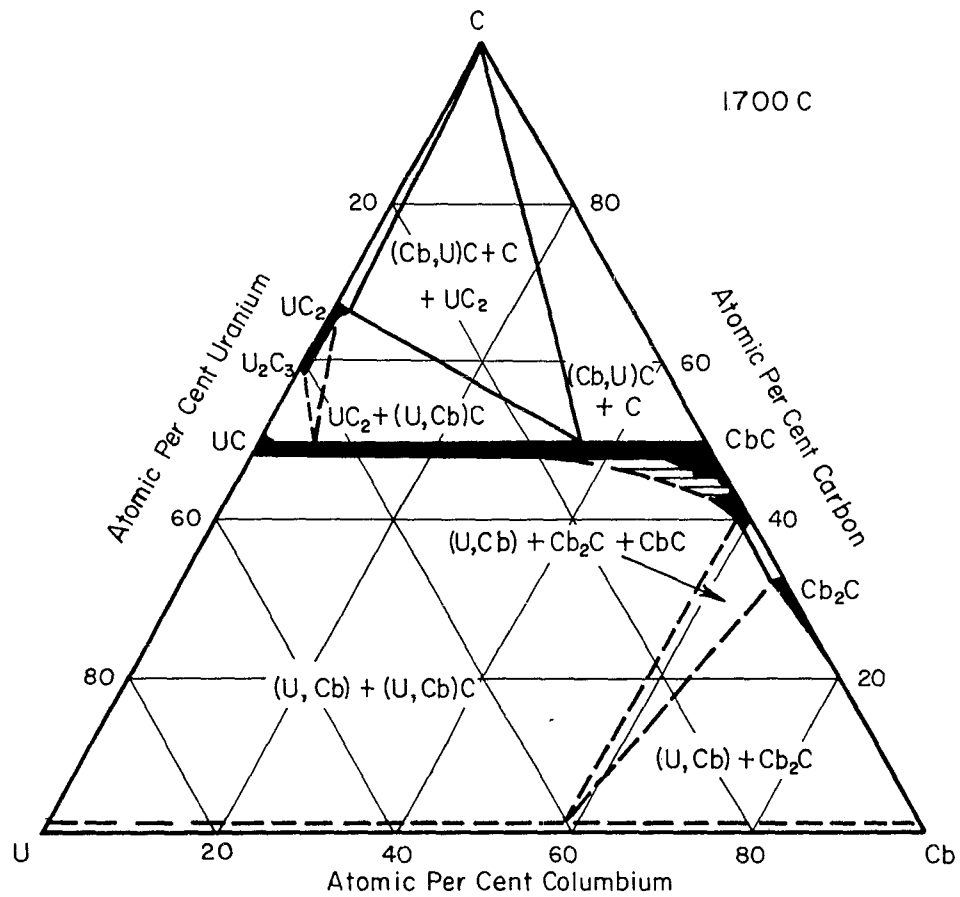

COLUMBIUM-CHROMIUM-NICKEL SYSTEM (1100 C)⁽²⁷³⁾

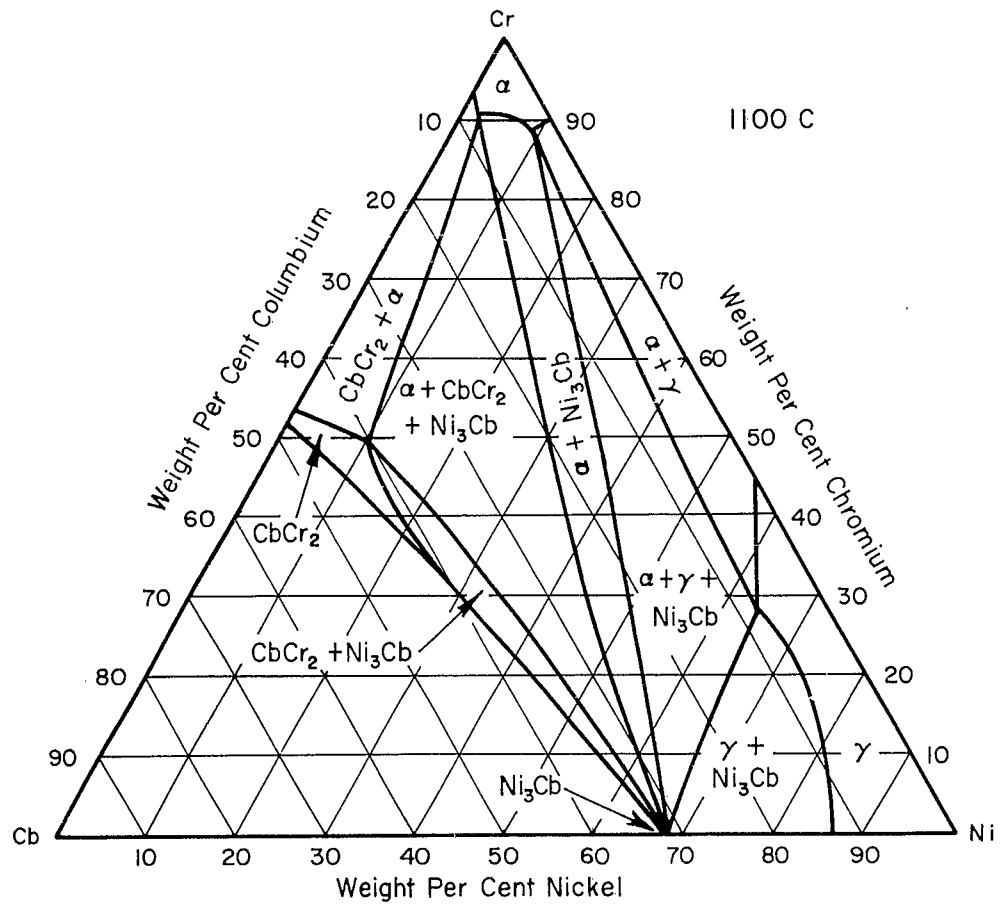


I
I
I
T
--
--
--
--
I
I
I
I
T
--
--
--
--
I
I
I




I
I
I
T
-
-
-
-
I
I
I
I
T
-
-
-
-
I
I
I


COLUMBIUM-CHROMIUM-SILICON SYSTEM (MELTING TEMPERATURES, C)⁽²⁷⁴⁾

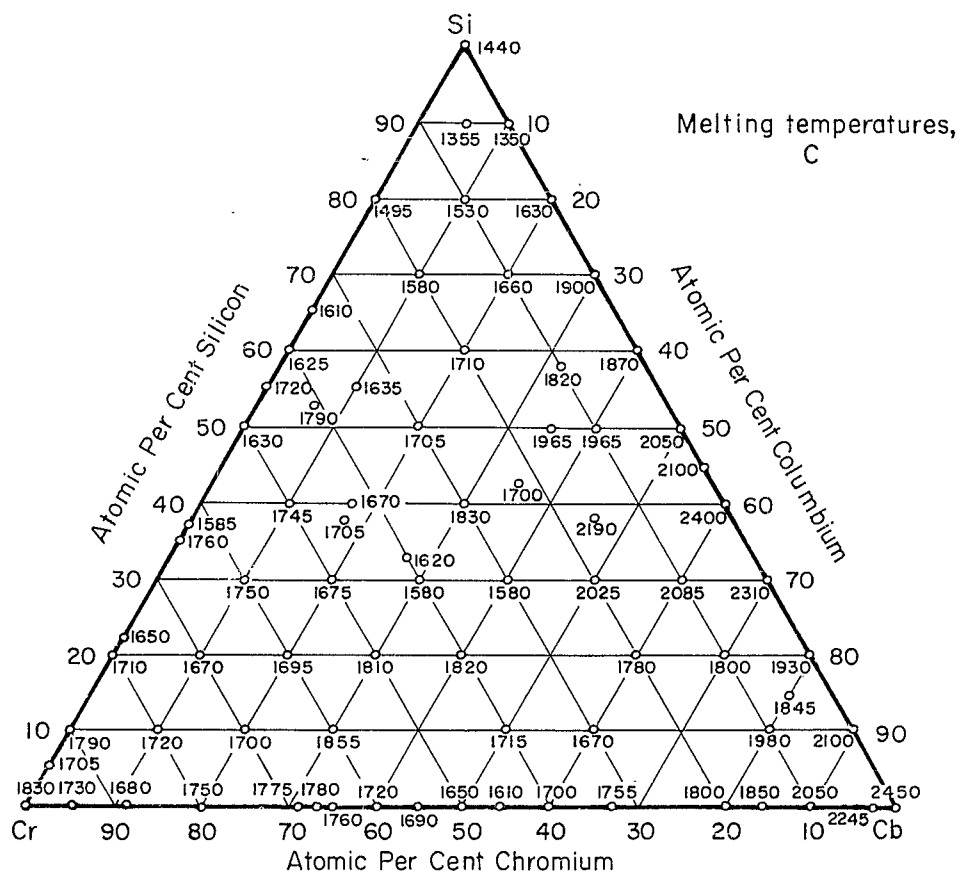


COLUMBIUM-CHROMIUM-VANADIUM SYSTEM (1450 C)⁽²⁷⁵⁾

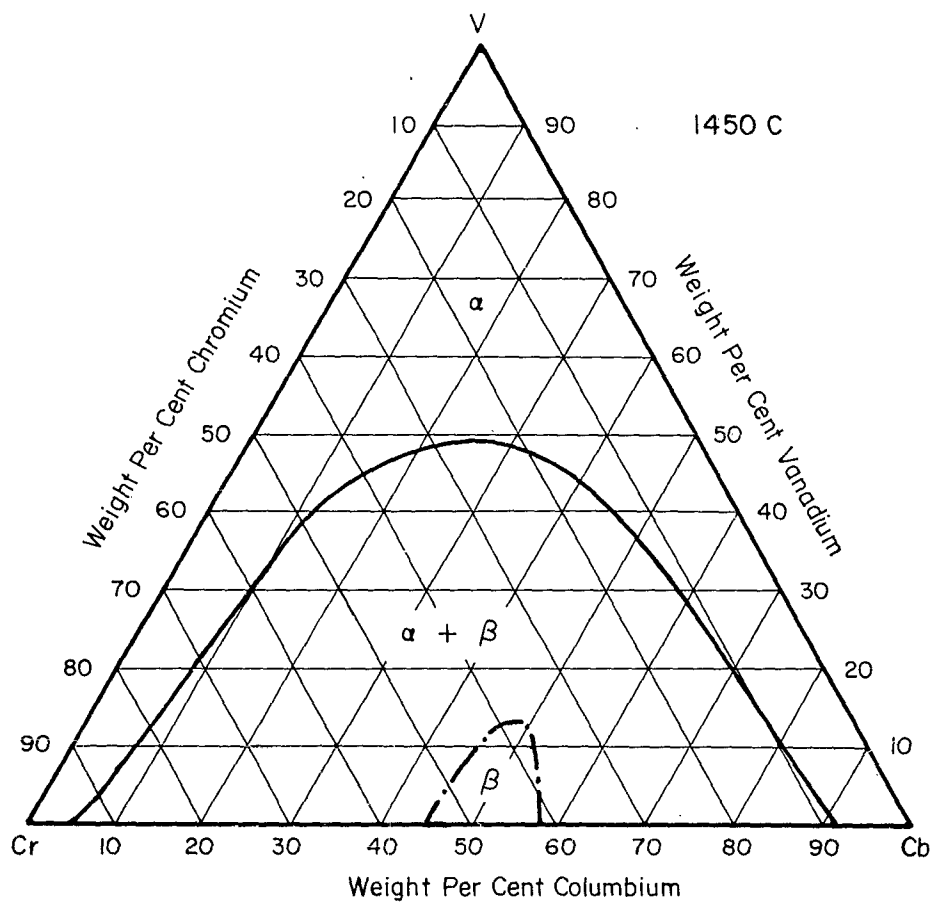


COLUMBIUM-IRON-PHOSPHORUS SYSTEM (ROOM TEMPERATURE)(276)

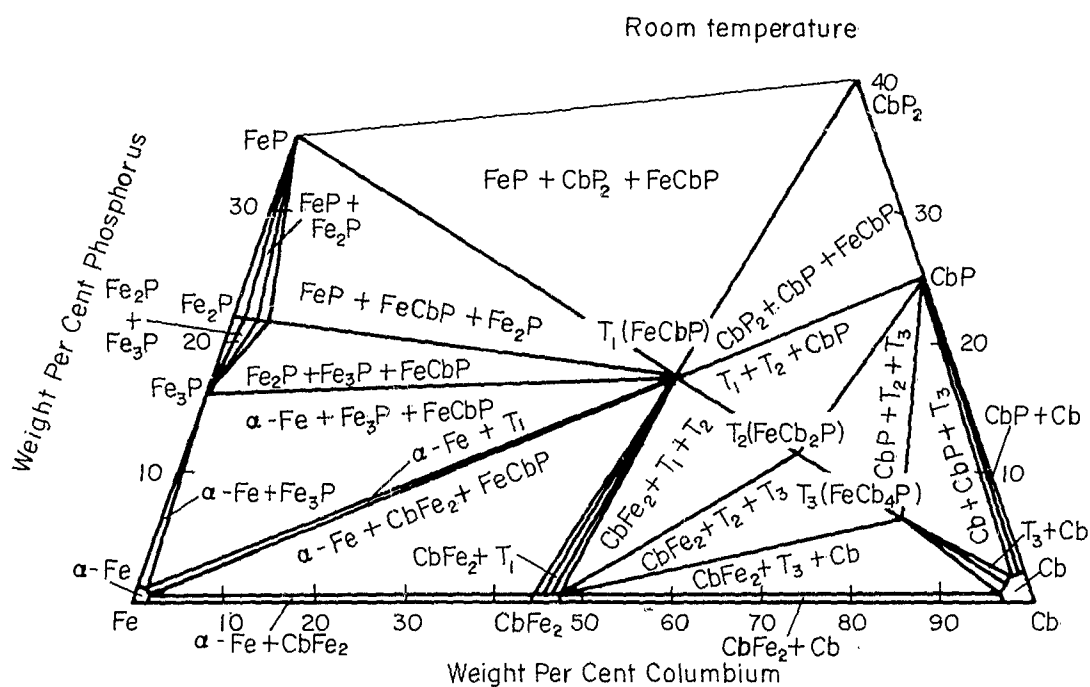


COLUMBIUM-MOLYBDENUM-CARBON SYSTEM (1900 C)(277)

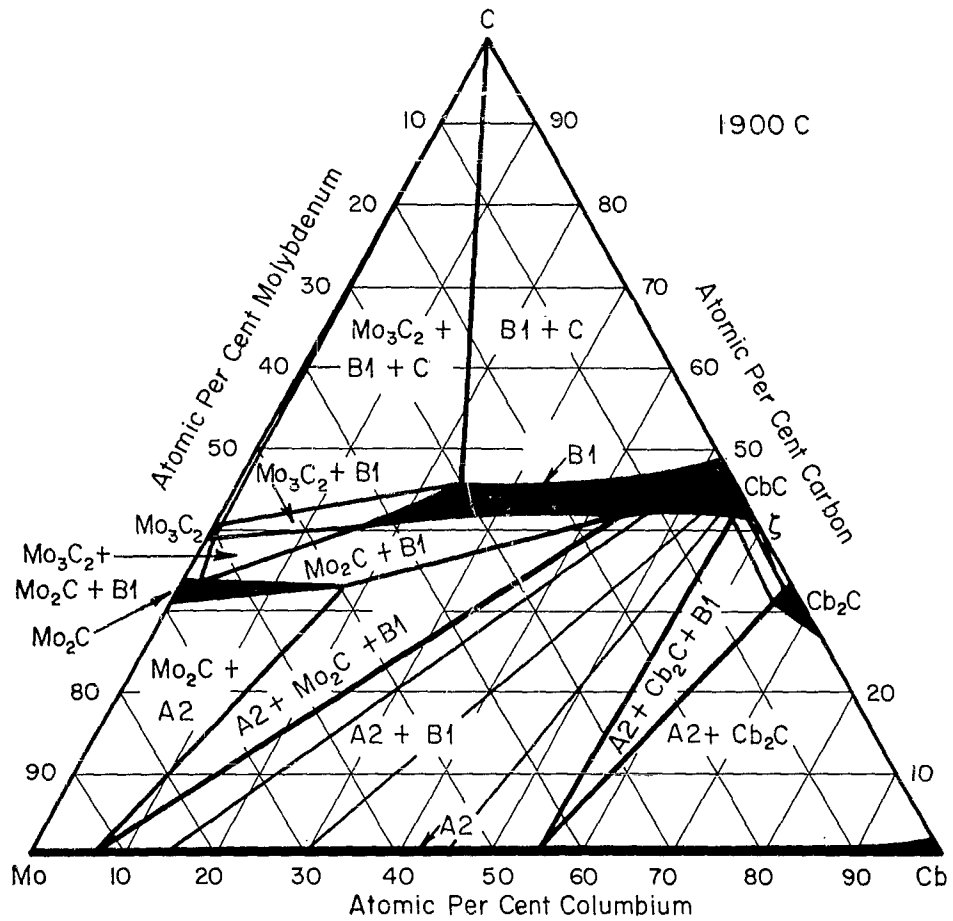


COLUMBIUM-MOLYBDENUM-CHROMIUM SYSTEM (1000 C)⁽²¹⁸⁾

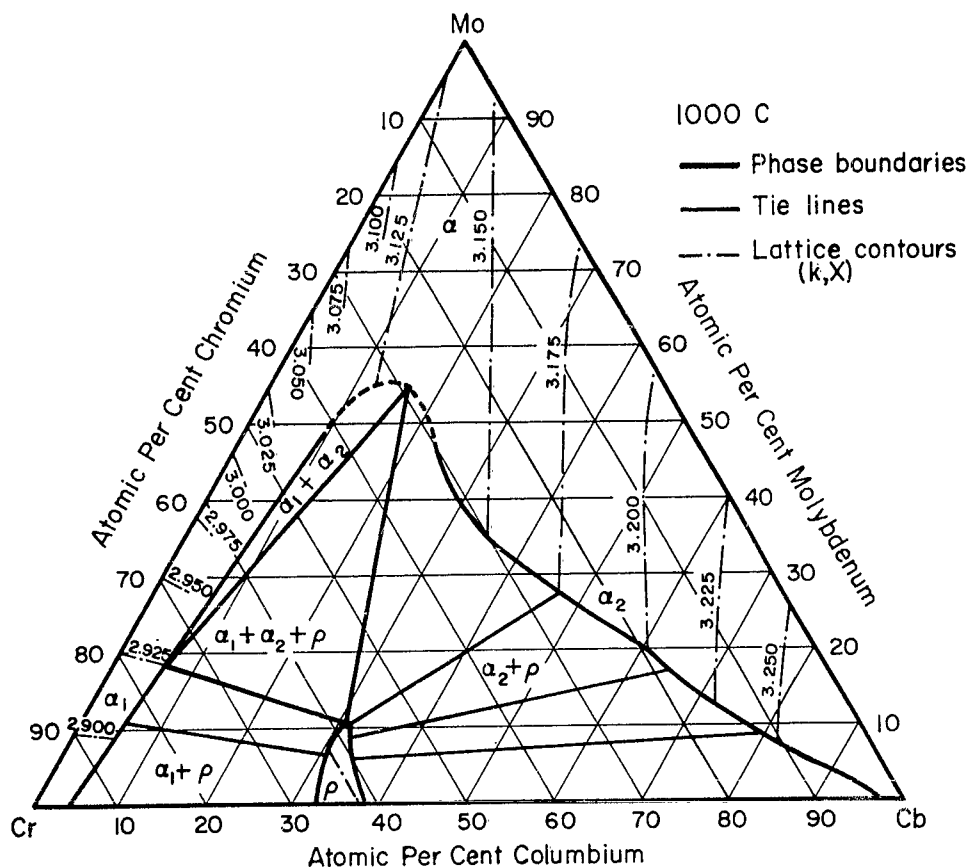


COLUMBIUM-MOLYBDENUM-CHROMIUM SYSTEM (1200 C)(279)

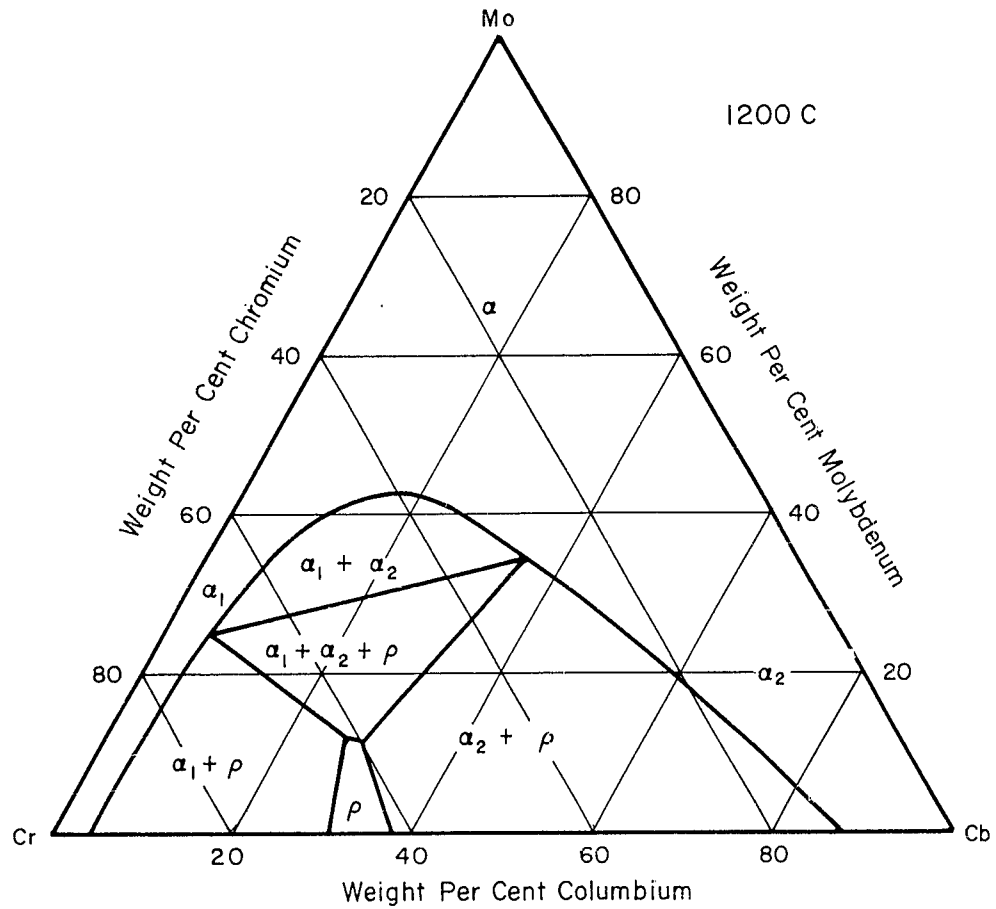

COLUMBIUM-MOLYBDENUM-CHROMIUM SYSTEM (LIQUIDUS ISOTHERMS)⁽²⁷⁸⁾

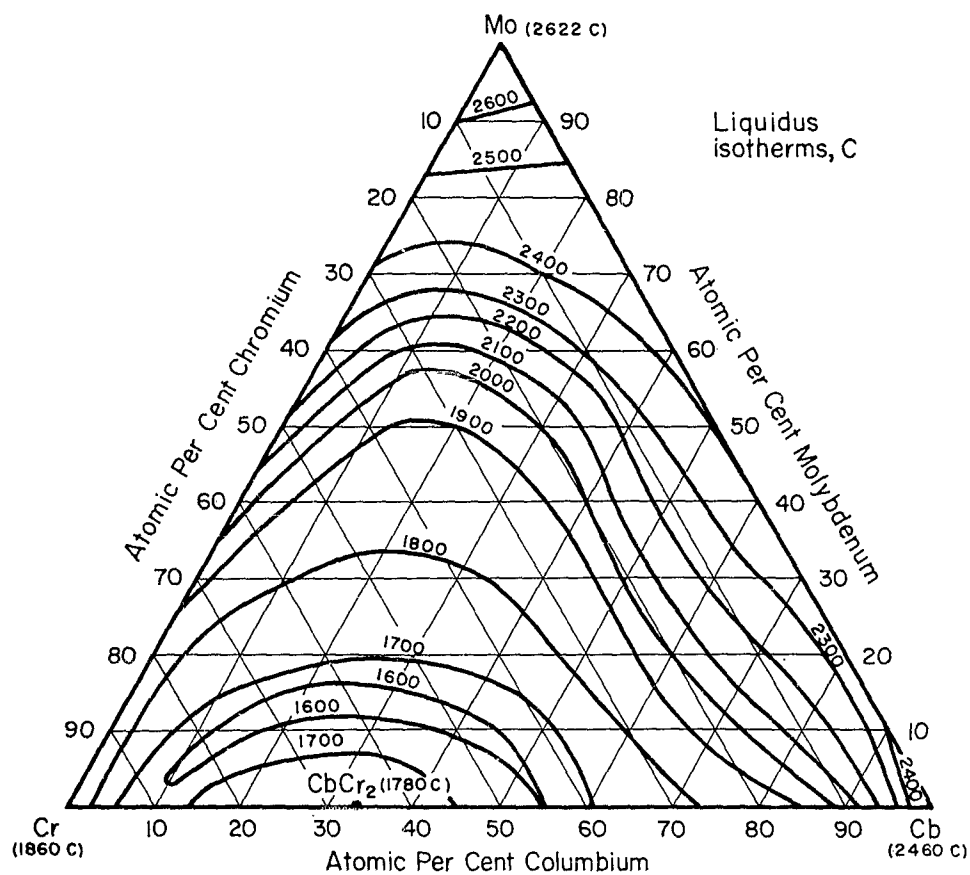


COLUMBIUM-MOLYBDENUM-URANIUM SYSTEM (700 C, 800 C, 900 C)(280)

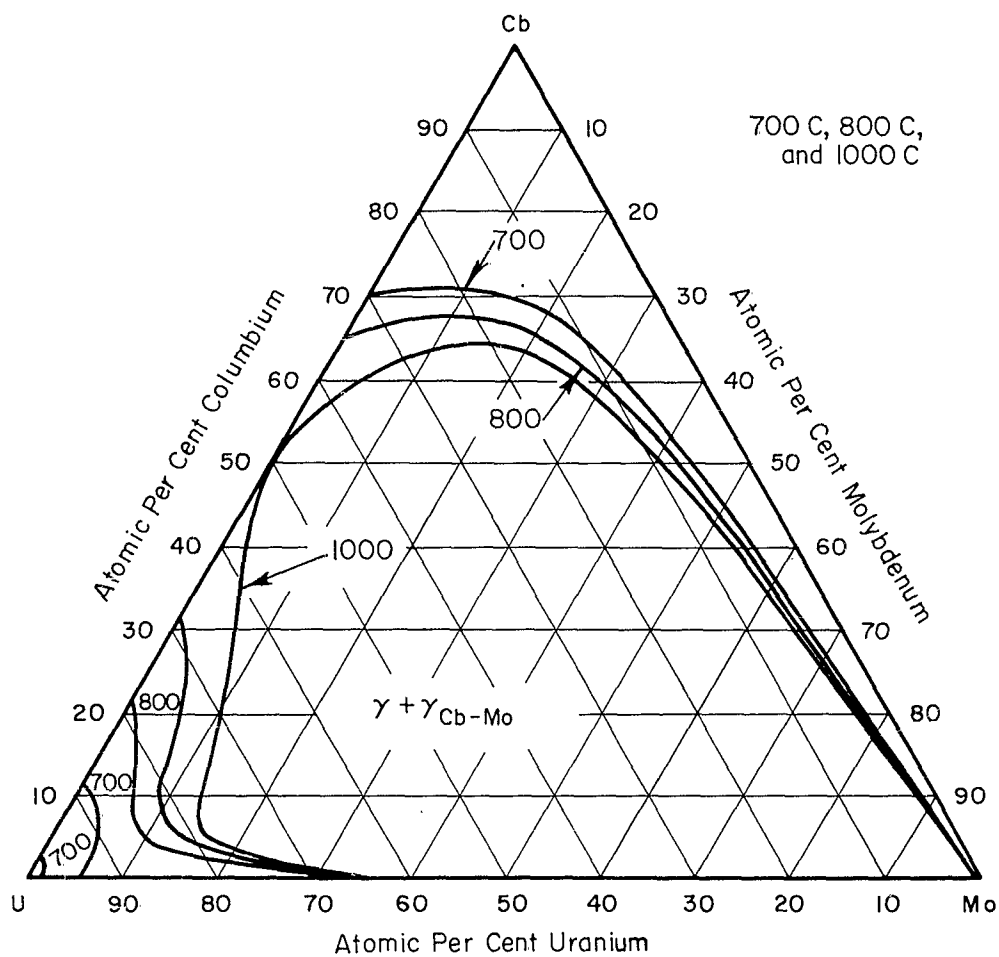


1
 2
 3
 4
 5
 6
 7
 8
 9
 10
 11
 12
 13
 14
 15
 16
 17
 18
 19
 20
 21
 22
 23
 24
 25
 26
 27
 28
 29
 30
 31
 32
 33
 34
 35
 36
 37
 38
 39
 40
 41
 42
 43
 44
 45
 46
 47
 48
 49
 50
 51
 52
 53
 54
 55
 56
 57
 58
 59
 60
 61
 62
 63
 64
 65
 66
 67
 68
 69
 70
 71
 72
 73
 74
 75
 76
 77
 78
 79
 80
 81
 82
 83
 84
 85
 86
 87
 88
 89
 90
 91
 92
 93
 94
 95
 96
 97
 98
 99
 100
 101
 102
 103
 104
 105
 106
 107
 108
 109
 110
 111
 112
 113
 114
 115
 116
 117
 118
 119
 120
 121
 122
 123
 124
 125
 126
 127
 128
 129
 130
 131
 132
 133
 134
 135
 136
 137
 138
 139
 140
 141
 142
 143
 144
 145
 146
 147
 148
 149
 150
 151
 152
 153
 154
 155
 156
 157
 158
 159
 160
 161
 162
 163
 164
 165
 166
 167
 168
 169
 170
 171
 172
 173
 174
 175
 176
 177
 178
 179
 180
 181
 182
 183
 184
 185
 186
 187
 188
 189
 190
 191
 192
 193
 194
 195
 196
 197
 198
 199
 200
 201
 202
 203
 204
 205
 206
 207
 208
 209
 210
 211
 212
 213
 214
 215
 216
 217
 218
 219
 220
 221
 222
 223
 224
 225
 226
 227
 228
 229
 230
 231
 232
 233
 234
 235
 236
 237
 238
 239
 240
 241
 242
 243
 244
 245
 246
 247
 248
 249
 250
 251
 252
 253
 254
 255
 256
 257
 258
 259
 260
 261
 262
 263
 264
 265
 266
 267
 268
 269
 270
 271
 272
 273
 274
 275
 276
 277
 278
 279
 280
 281
 282
 283
 284
 285
 286
 287
 288
 289
 290
 291
 292
 293
 294
 295
 296
 297
 298
 299
 300
 301
 302
 303
 304
 305
 306
 307
 308
 309
 310
 311
 312
 313
 314
 315
 316
 317
 318
 319
 320
 321
 322
 323
 324
 325
 326
 327
 328
 329
 330
 331
 332
 333
 334
 335
 336
 337
 338
 339
 340
 341
 342
 343
 344
 345
 346
 347
 348
 349
 350
 351
 352
 353
 354
 355
 356
 357
 358
 359
 360
 361
 362
 363
 364
 365
 366
 367
 368
 369
 370
 371
 372
 373
 374
 375
 376
 377
 378
 379
 380
 381
 382
 383
 384
 385
 386
 387
 388
 389
 390
 391
 392
 393
 394
 395
 396
 397
 398
 399
 400
 401
 402
 403
 404
 405
 406
 407
 408
 409
 410
 411
 412
 413
 414
 415
 416
 417
 418
 419
 420
 421
 422
 423
 424
 425
 426
 427
 428
 429
 430
 431
 432
 433
 434
 435
 436
 437
 438
 439
 440
 441
 442
 443
 444
 445
 446
 447
 448
 449
 450
 451
 452
 453
 454
 455
 456
 457
 458
 459
 460
 461
 462
 463
 464
 465
 466
 467
 468
 469
 470
 471
 472
 473
 474
 475
 476
 477
 478
 479
 480
 481
 482
 483
 484
 485
 486
 487
 488
 489
 490
 491
 492
 493
 494
 495
 496
 497
 498
 499
 500
 501
 502
 503
 504
 505
 506
 507
 508
 509
 510
 511
 512
 513
 514
 515
 516
 517
 518
 519
 520
 521
 522
 523
 524
 525




COLUMBIUM-MOLYBDENUM-URANIUM SYSTEM (1200 C)⁽³¹⁸⁾

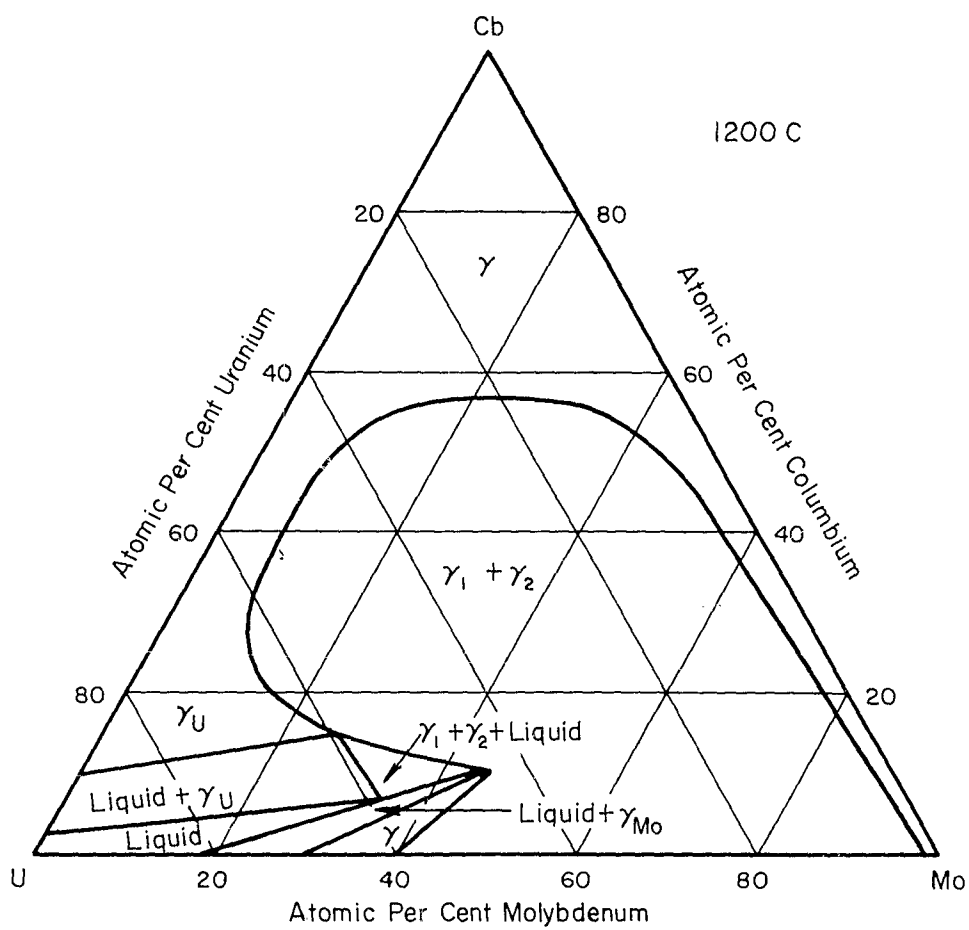


COLUMBIUM-MOLYBDENUM-URANIUM SYSTEM (1300 C)(318)

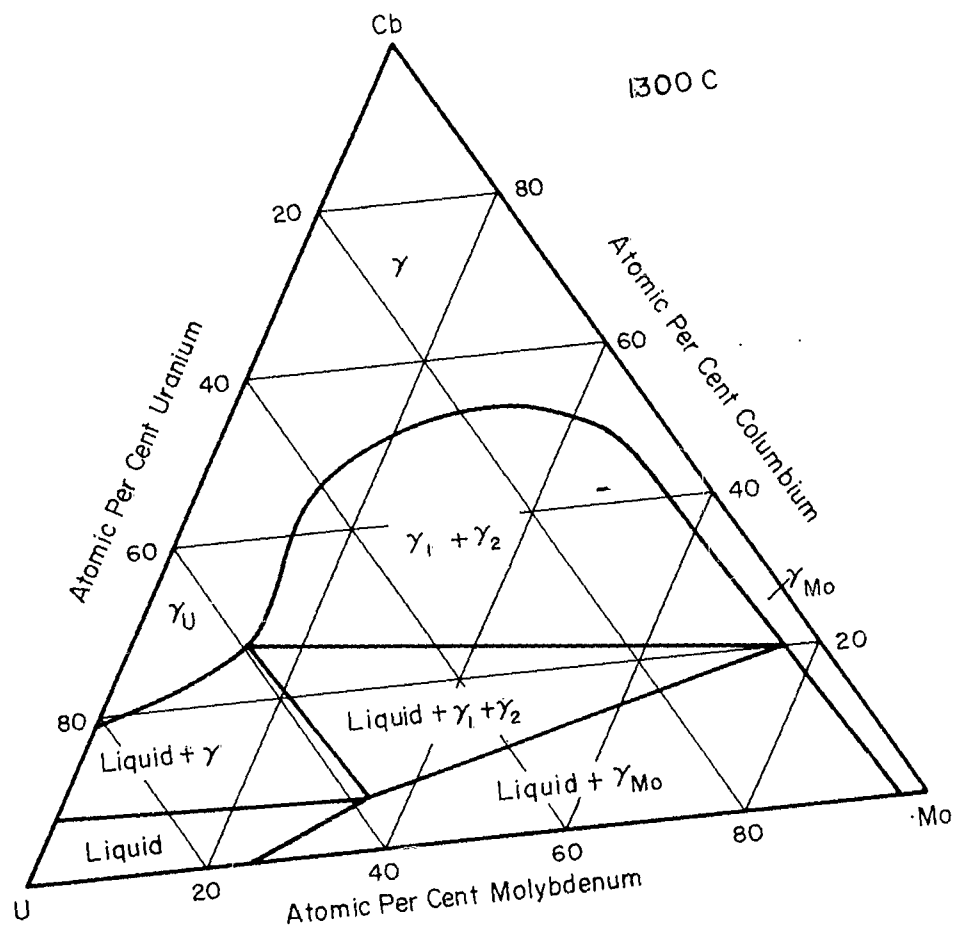


COLUMBIUM-NITROGEN-OXYGEN SYSTEM (1500 C)⁽²⁸¹⁾

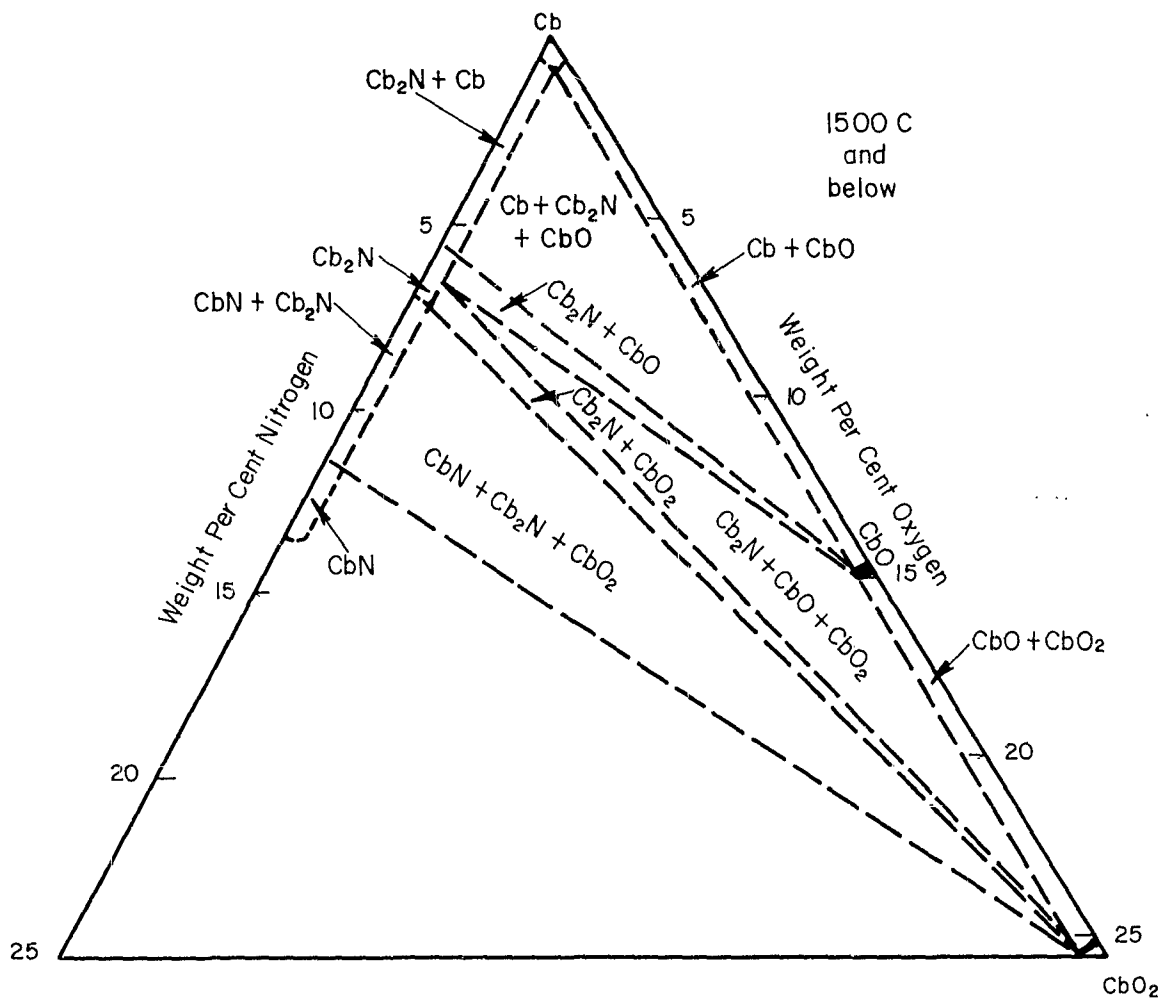


COLUMBIUM-OXYGEN-TITANIUM SYSTEM (1500 C)⁽³⁰¹⁾

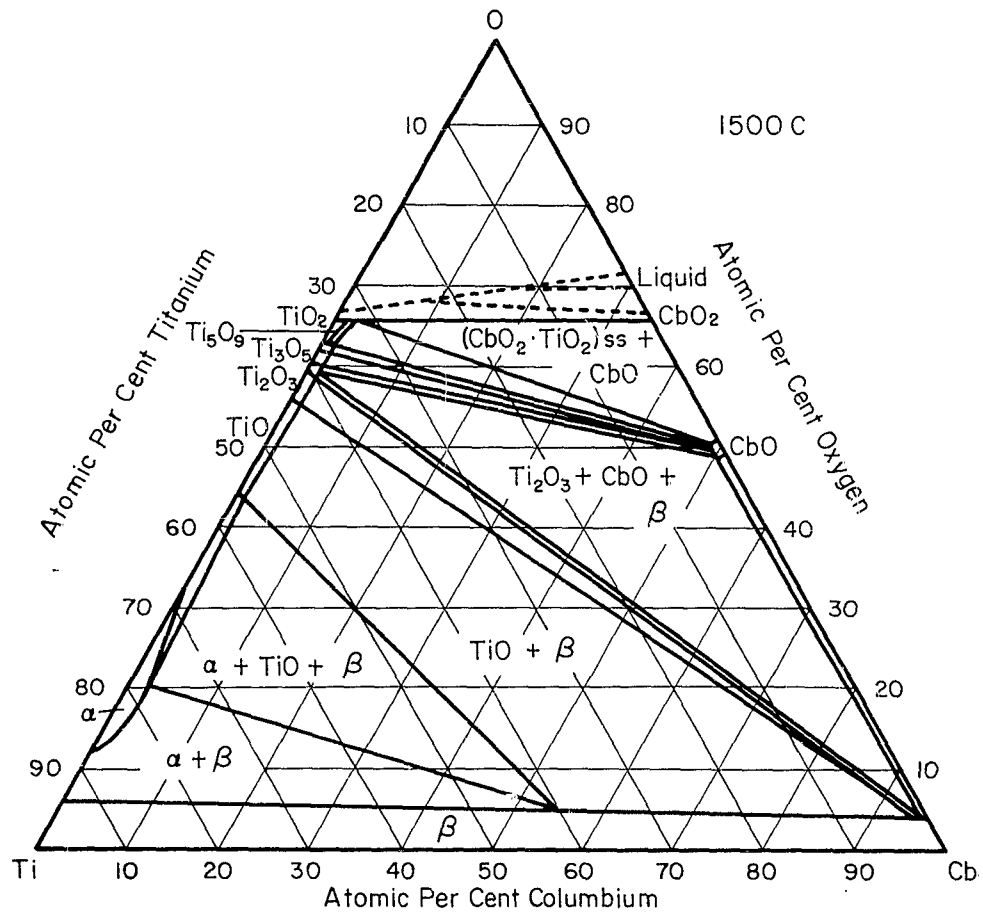


COLUMBIUM-OXYGEN-ZIRCONIUM SYSTEM (1500 C)⁽³⁰¹⁾

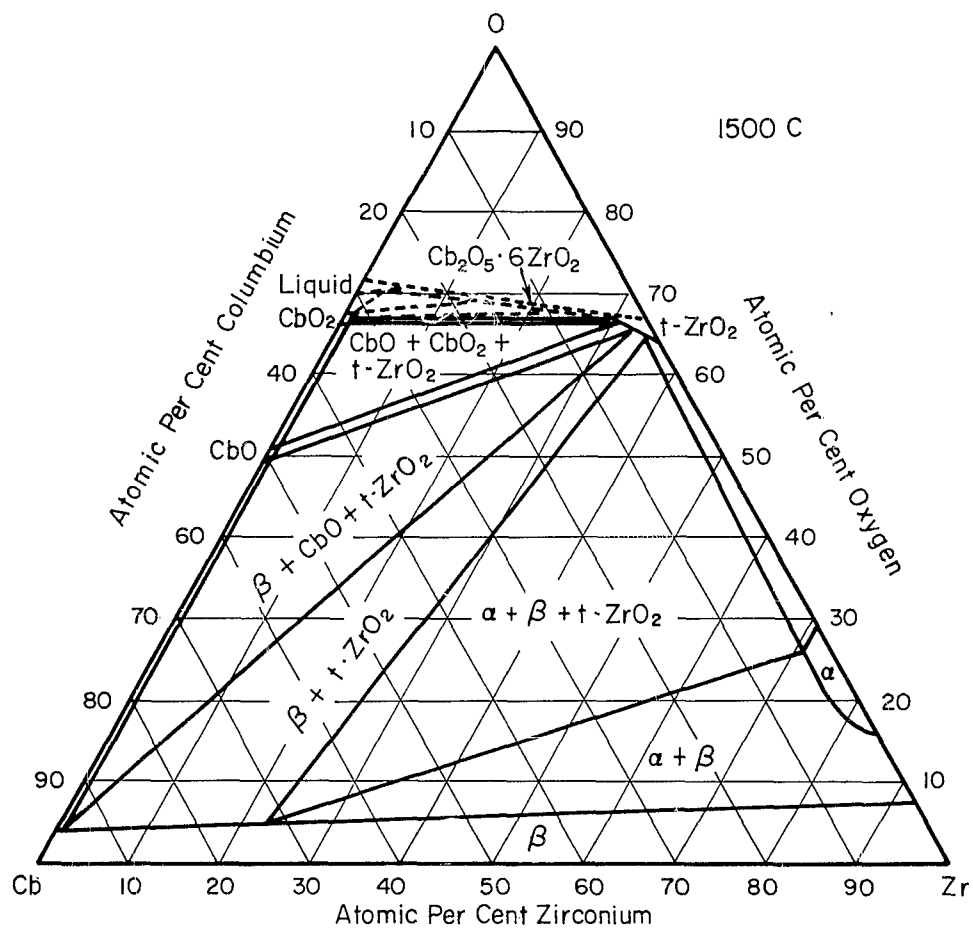


COLUMBIUM-SILICON-VANADIUM SYSTEM (SCHEMATIC)⁽³¹⁵⁾

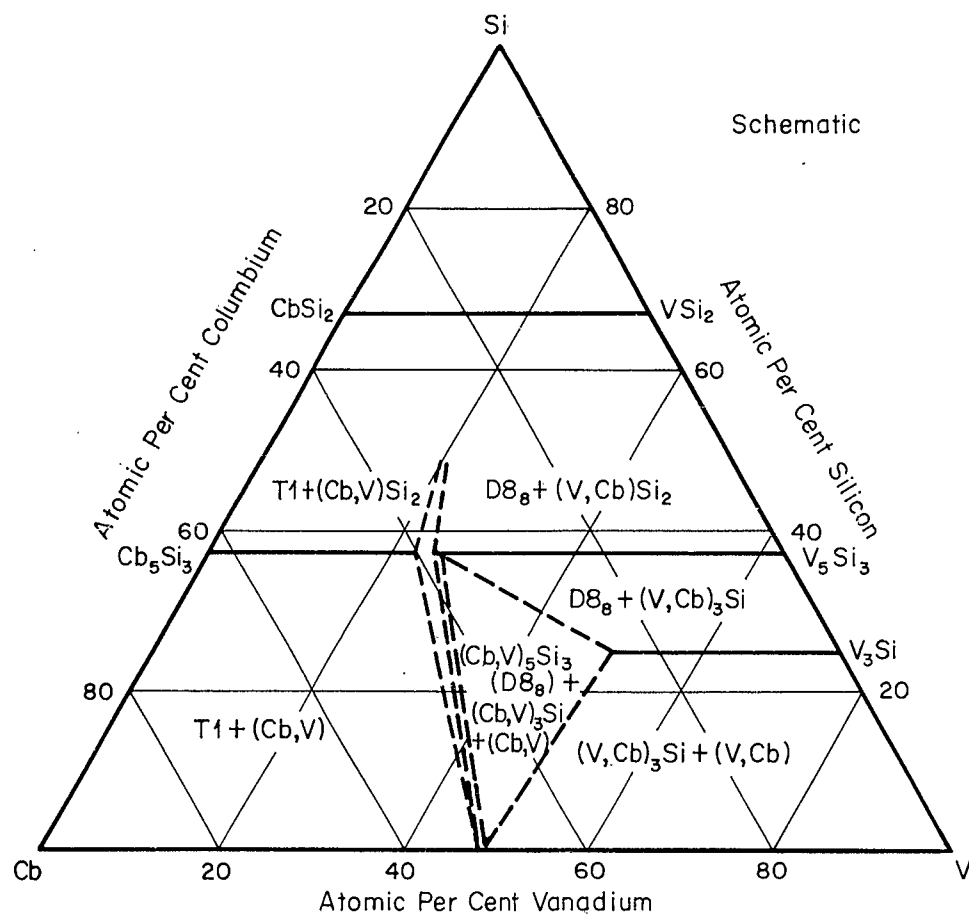


COLUMBIUM-TITANIUM-ZIRCONIUM SYSTEM (MELTING TEMPERATURES, C)⁽²⁸²⁾

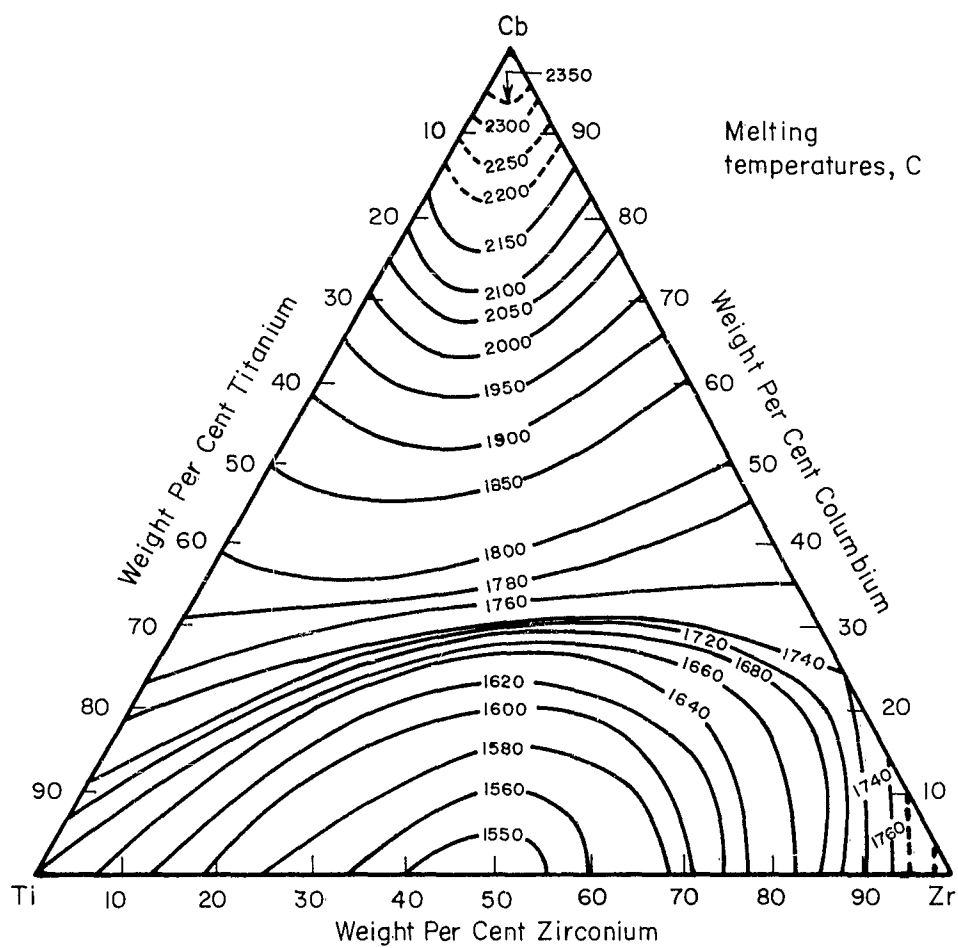


COLUMBIUM-URANIUM-ZIRCONIUM SYSTEM (1000 C)(280)

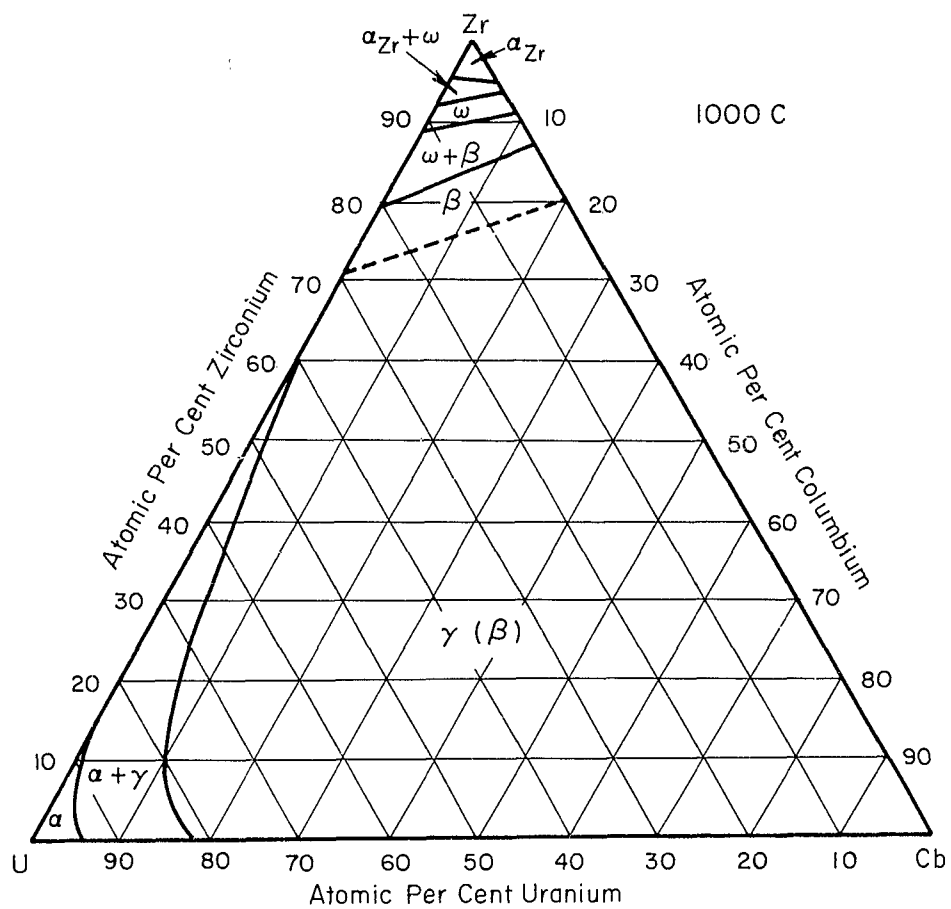


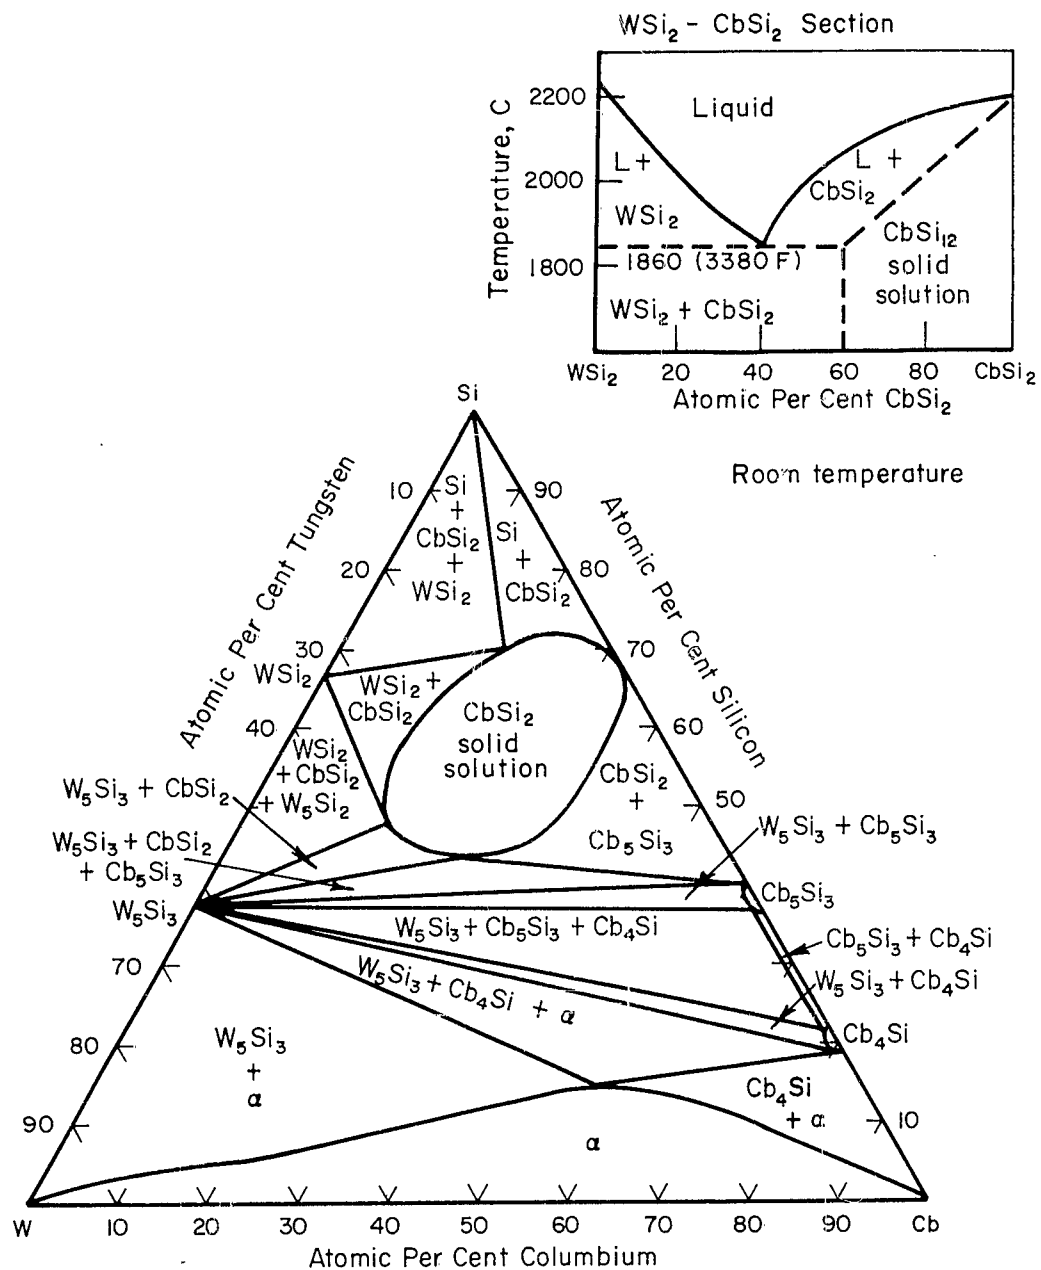COLUMBIUM-TUNGSTEN-SILICON SYSTEM (ROOM TEMPERATURE)⁽³²¹⁾


COLUMBIUM-TUNGSTEN-ZIRCONIUM SYSTEM (1100 C)⁽³¹⁹⁾

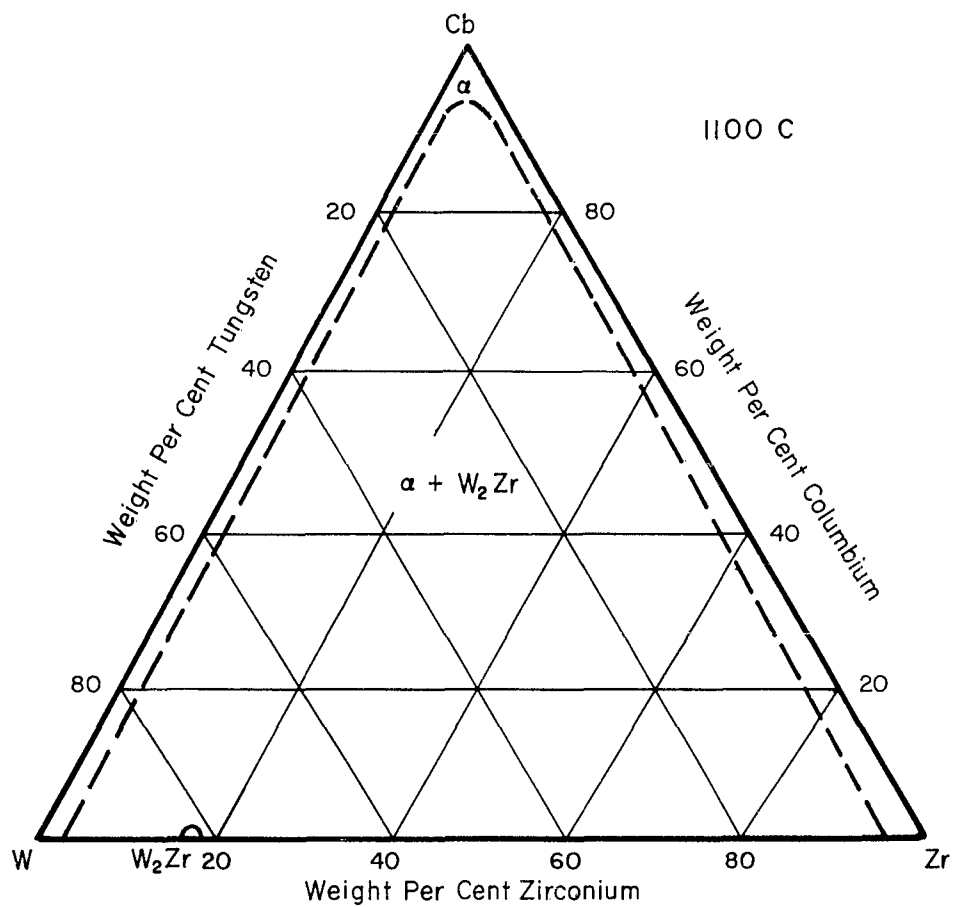


COLUMBIUM-TUNGSTEN-ZIRCONIUM SYSTEM (1600 C)⁽³¹⁹⁾

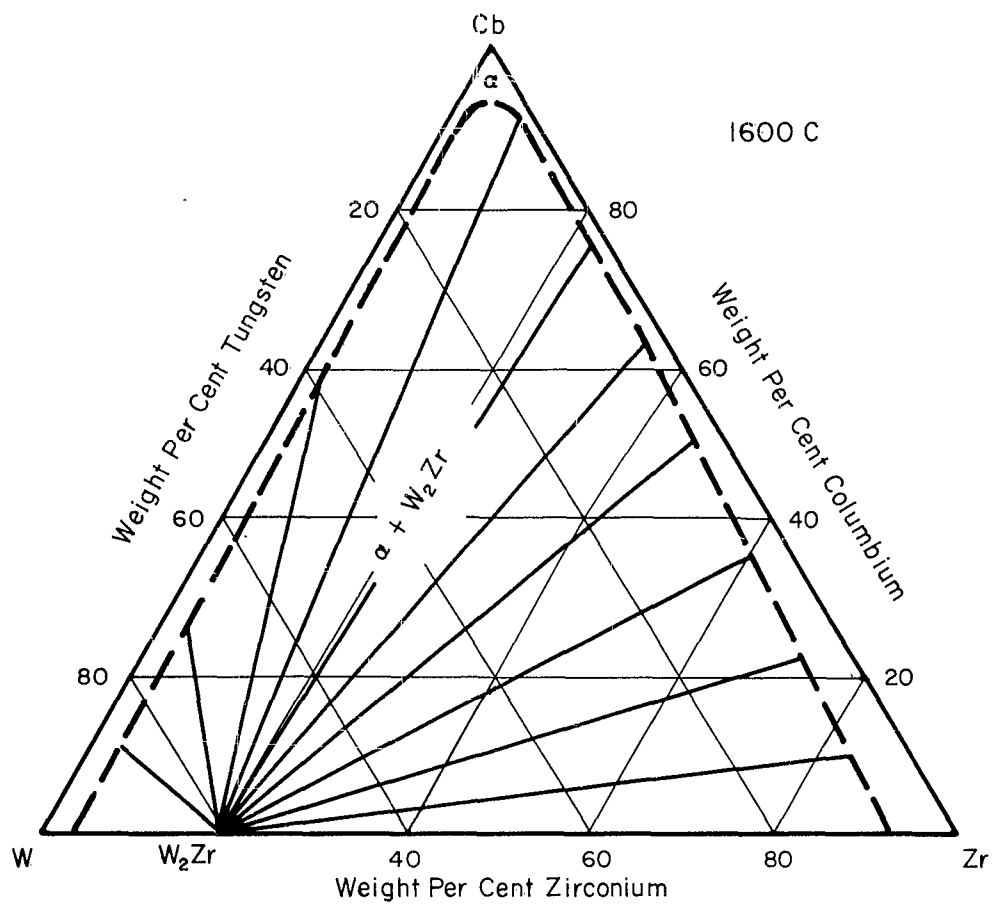


COLUMBIUM-TUNGSTEN-ZIRCONIUM SYSTEM (1800 C)(319)

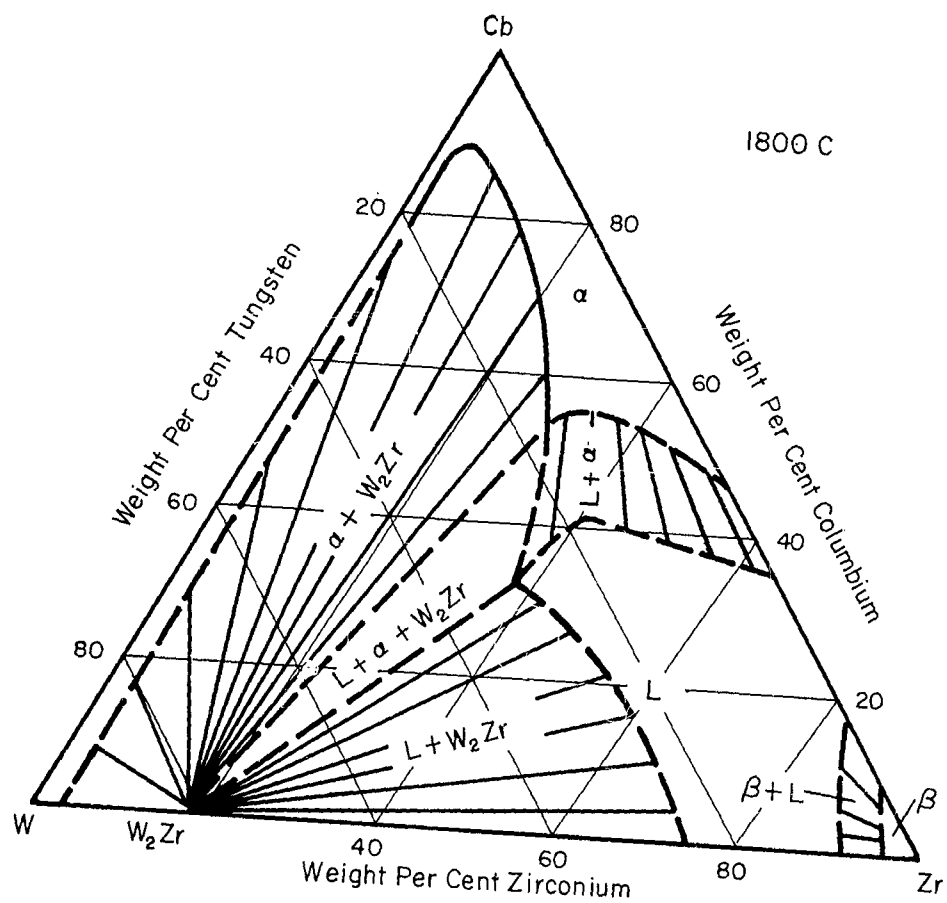


COLUMBIUM-TUNGSTEN-ZIRCONIUM SYSTEM (2000 C)⁽³¹⁹⁾

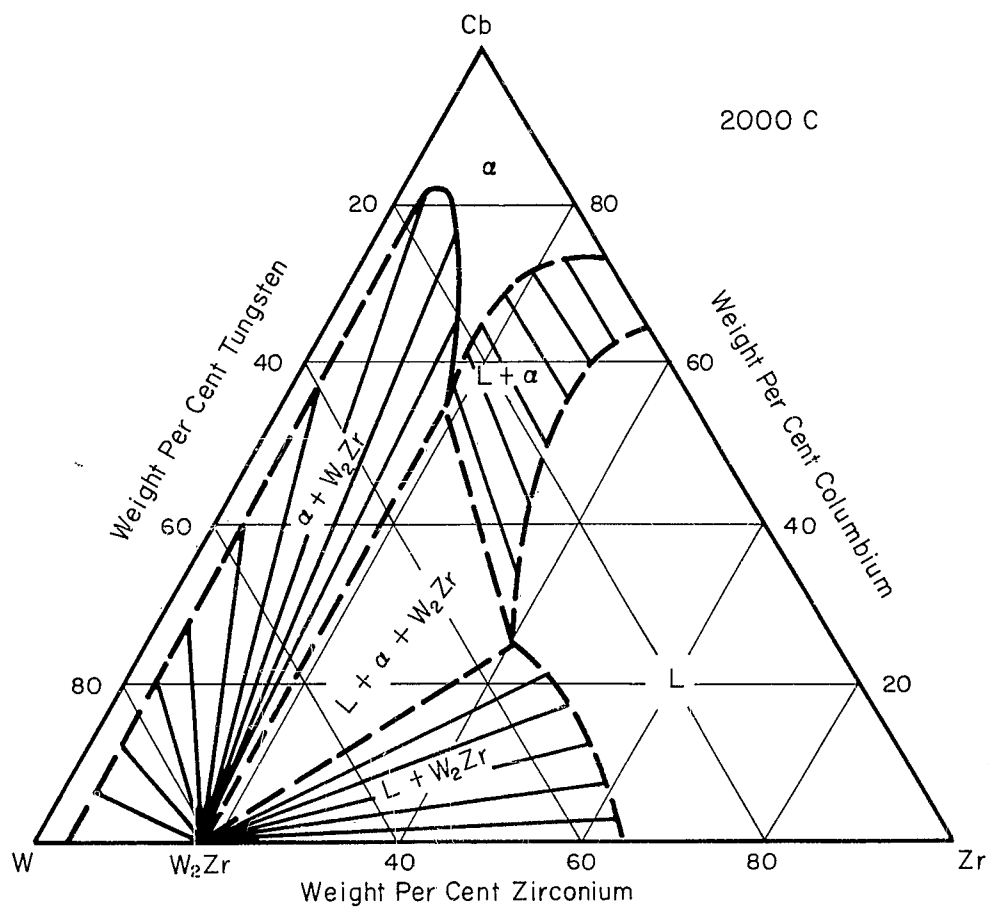


MOLYBDENUM-ALUMINUM-NICKEL SYSTEM (1175 C)(283)

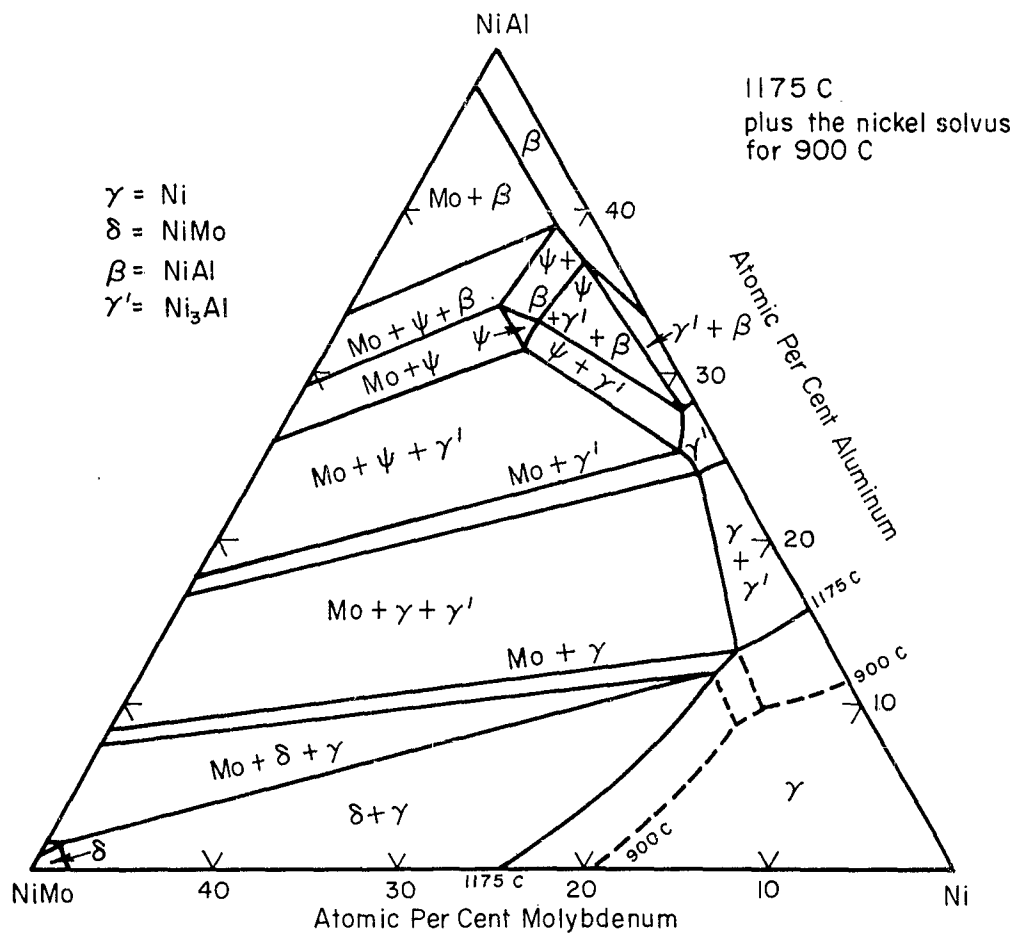

MOLYBDENUM-ALUMINUM-SILICON SYSTEM (1600 C)(268)

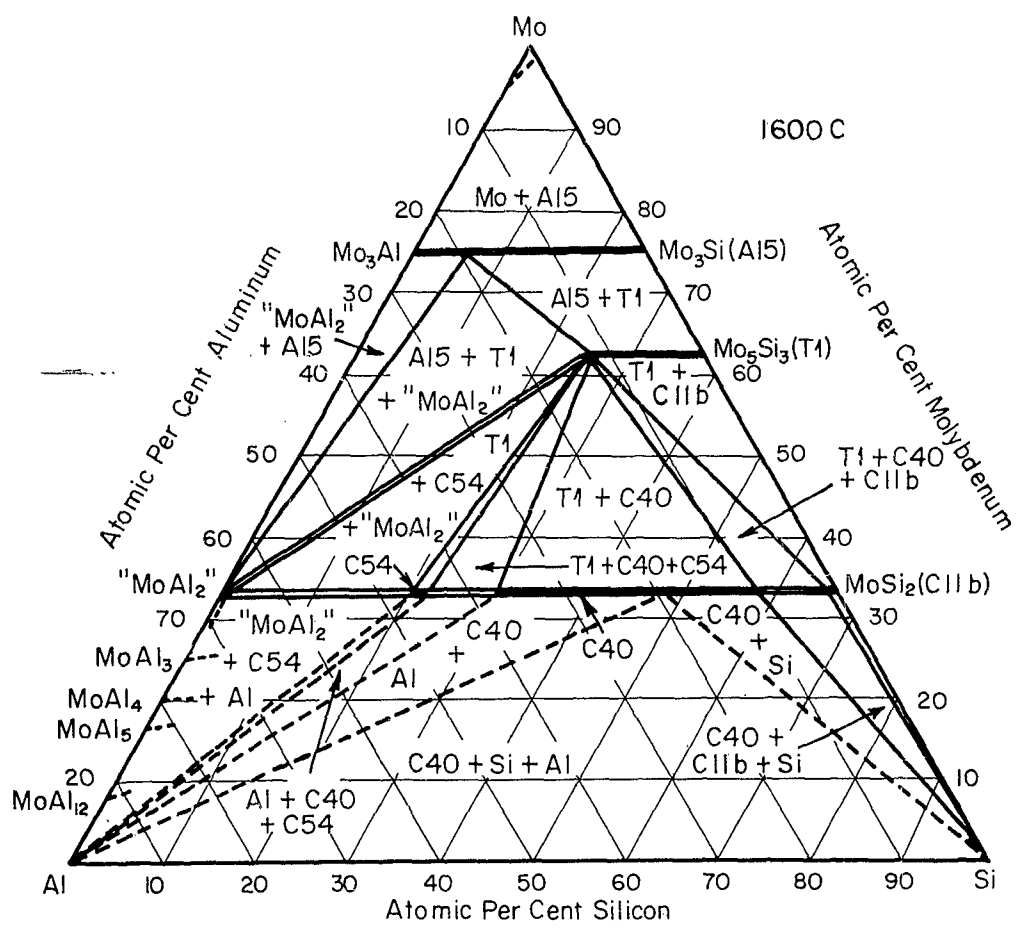


MOLYBDENUM-BORON-NICKEL SYSTEM (1000 C)⁽²⁸⁴⁾

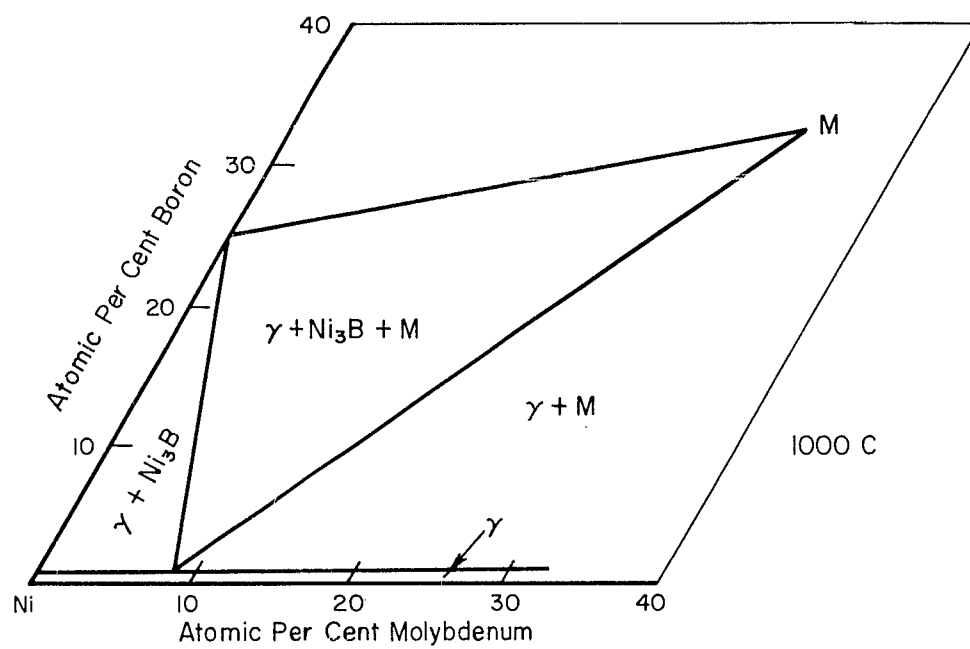


M = NiMoB


MOLYBDENUM-BORON-TITANIUM SYSTEM (1200 C)(285)

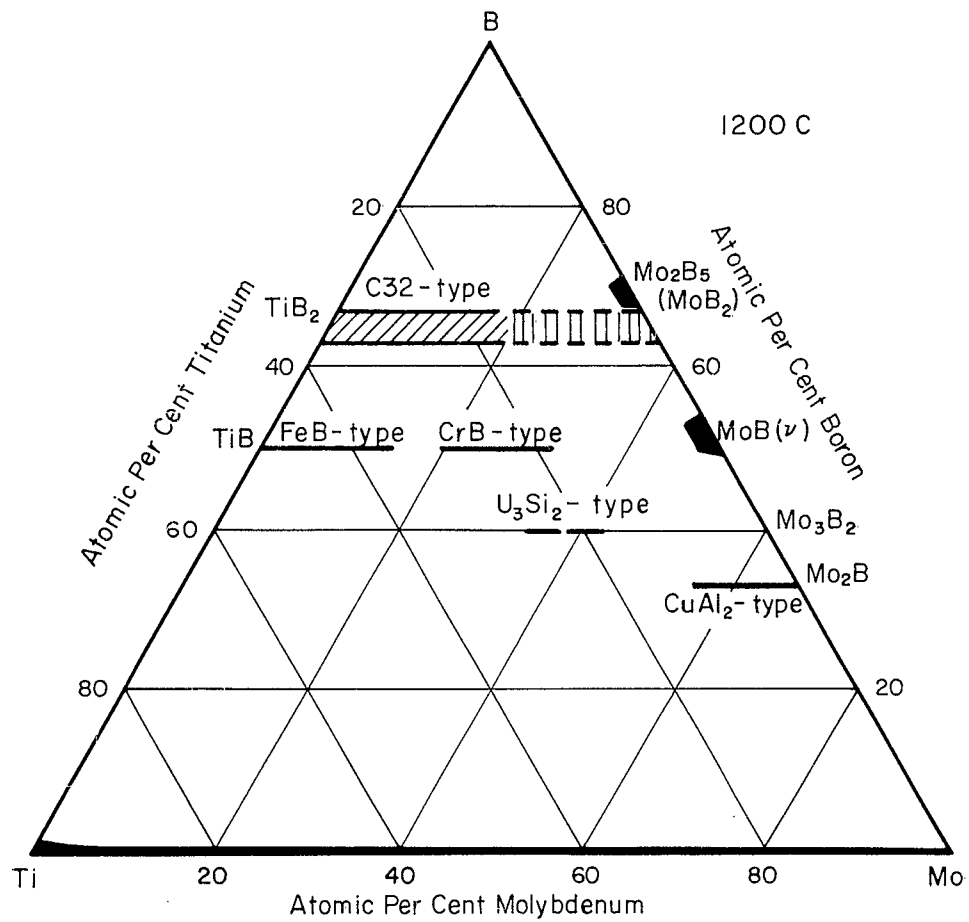

MOLYBDENUM-BORON-TITANIUM SYSTEM (1700 C)(285)

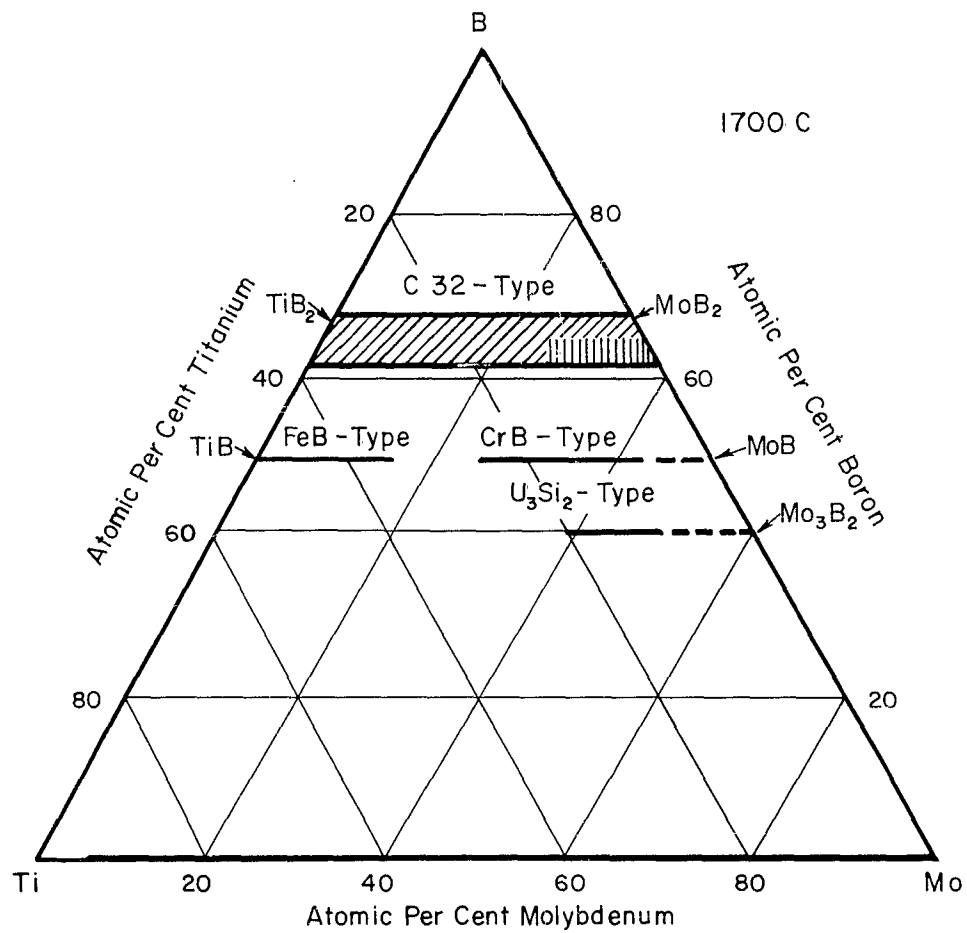


MOLYBDENUM-HAFNIUM-RHENIUM SYSTEM (1600 C)(250)

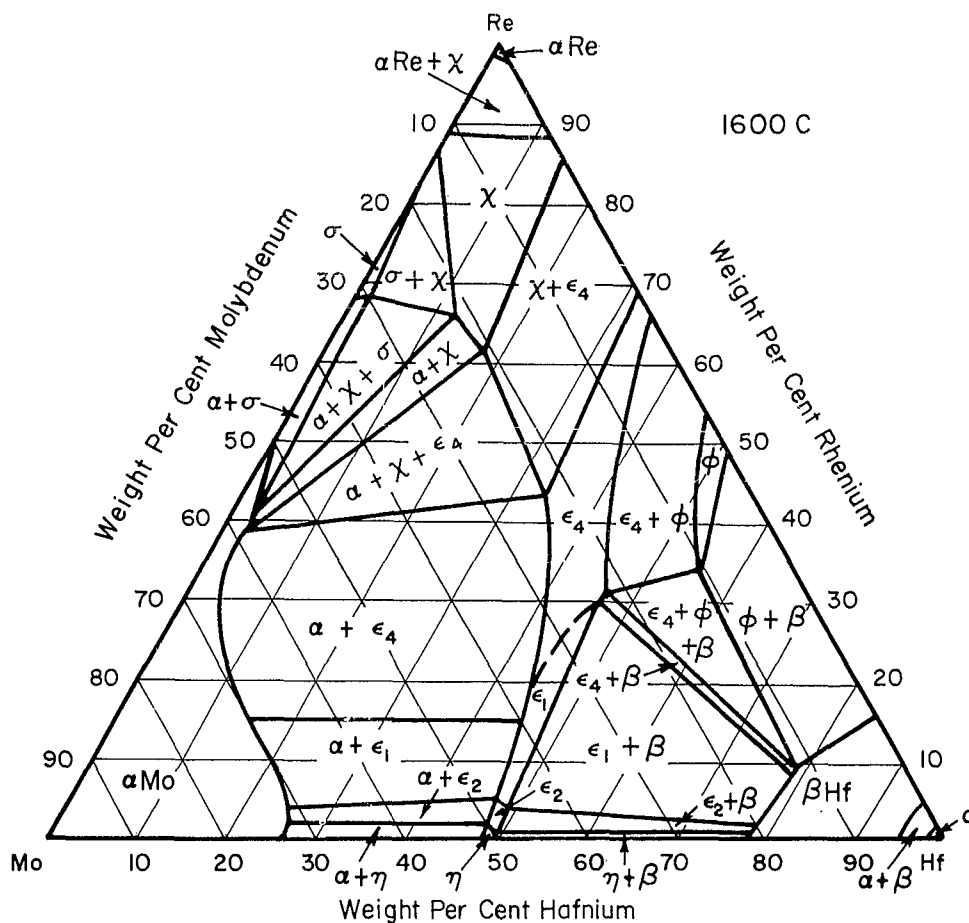


The phase ϕ has a tetragonal structure with $a = 8.90 \text{ \AA}$ and $c = 13.97 \text{ \AA}$; this phase forms peritectically at 2745 C and about 47.5 per cent hafnium in the binary rhenium-hafnium system. An intermediate Laves phase ϵ_4 (based on Re_2Hf) has the C14-MgZn₂ type of structure with $a = 5.239 \text{ \AA}$, $c = 8.584 \text{ \AA}$, and $c/a = 1.638$.(250)


MOLYBDENUM-HAFNIUM-RHENIUM SYSTEM (2000 C)(250)

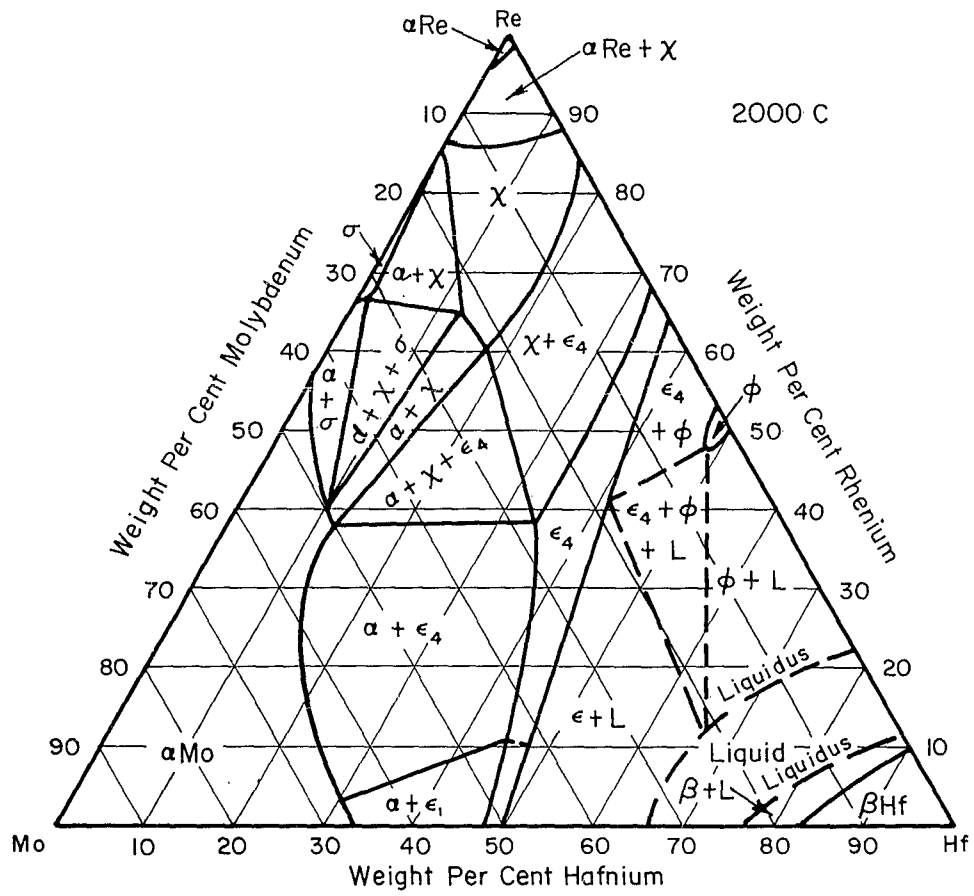


MOLYBDENUM-HAFNIUM-RHENIUM SYSTEM (2400 C)(250)

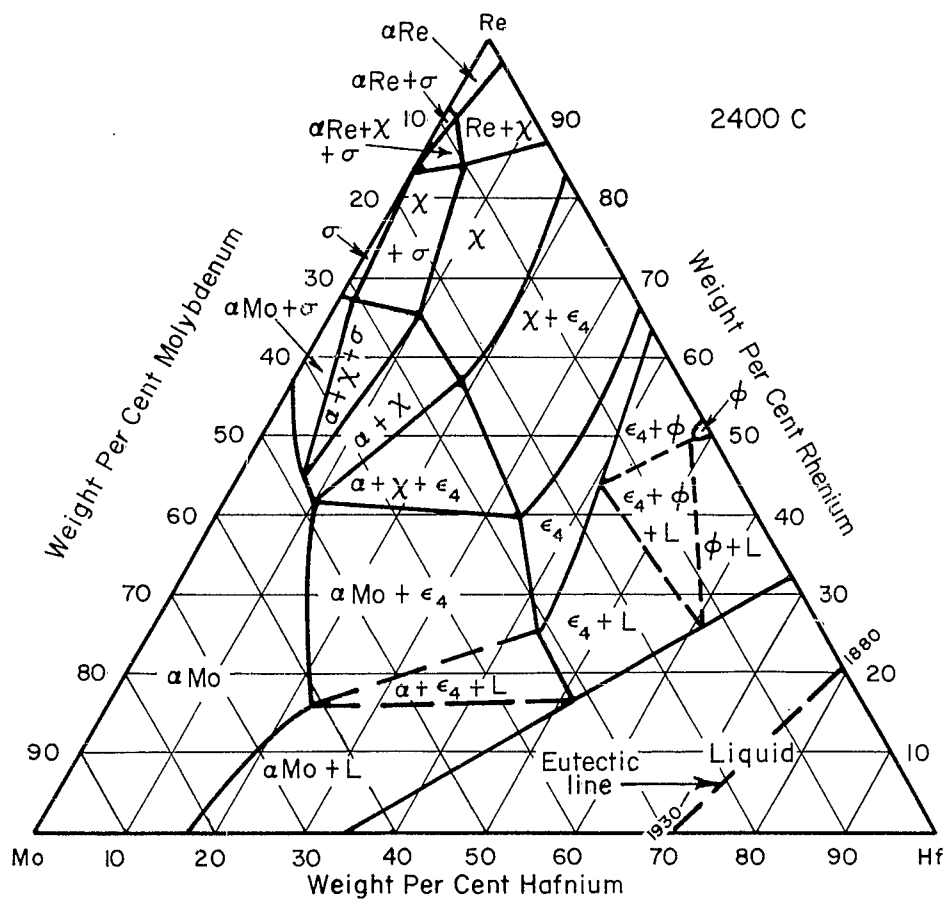


MOLYBDENUM-IRON-PHOSPHORUS SYSTEM (ROOM TEMPERATURE)⁽³¹³⁾

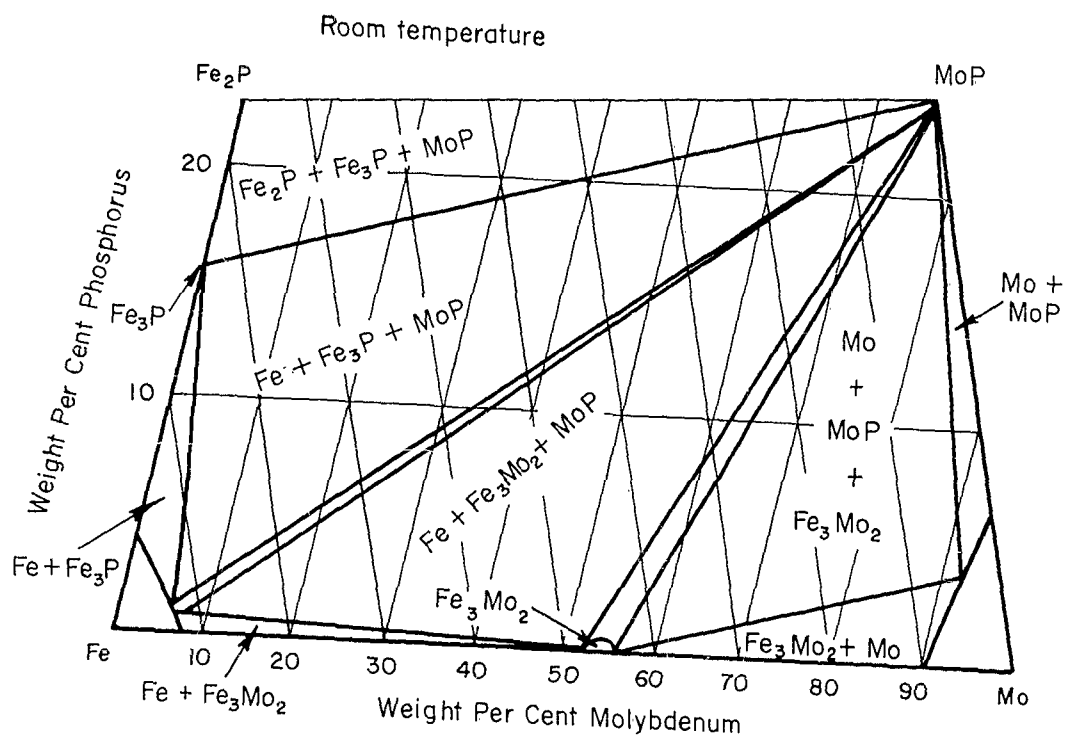


MOLYBDENUM-IRON-SILICON SYSTEM (20 C)(286)

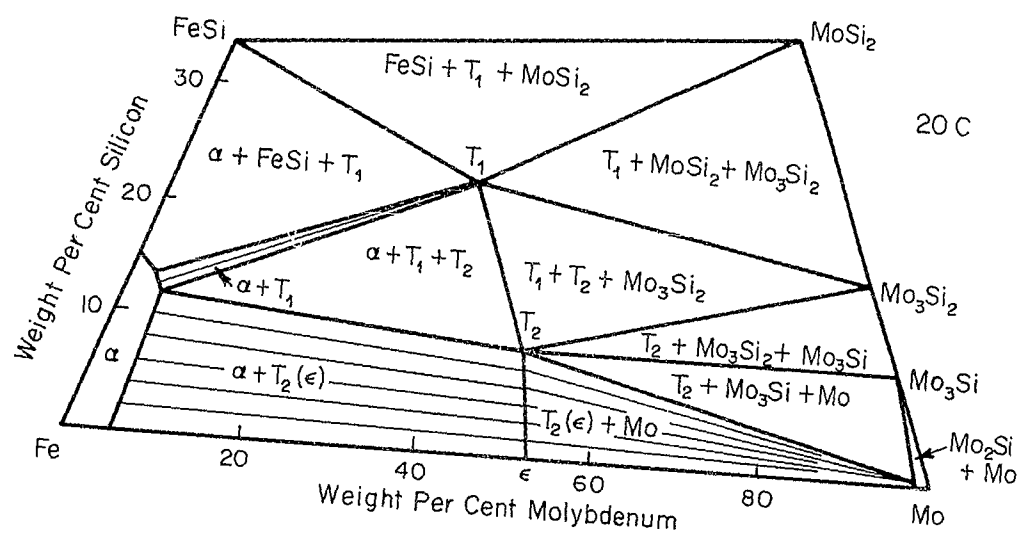


MOLYBDENUM-NICKEL-SILICON SYSTEM (1100 C)(283)

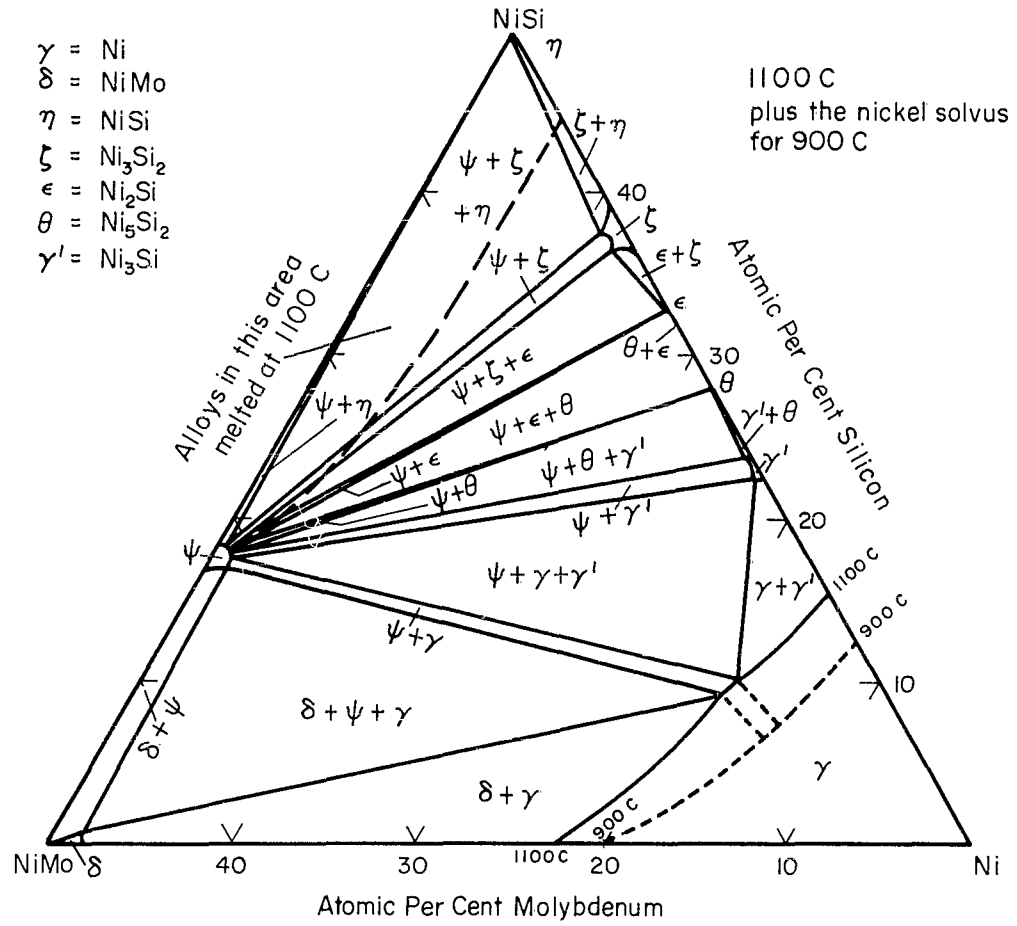


MOLYBDENUM-NICKEL-TITANIUM SYSTEM (1175 C)⁽³¹²⁾

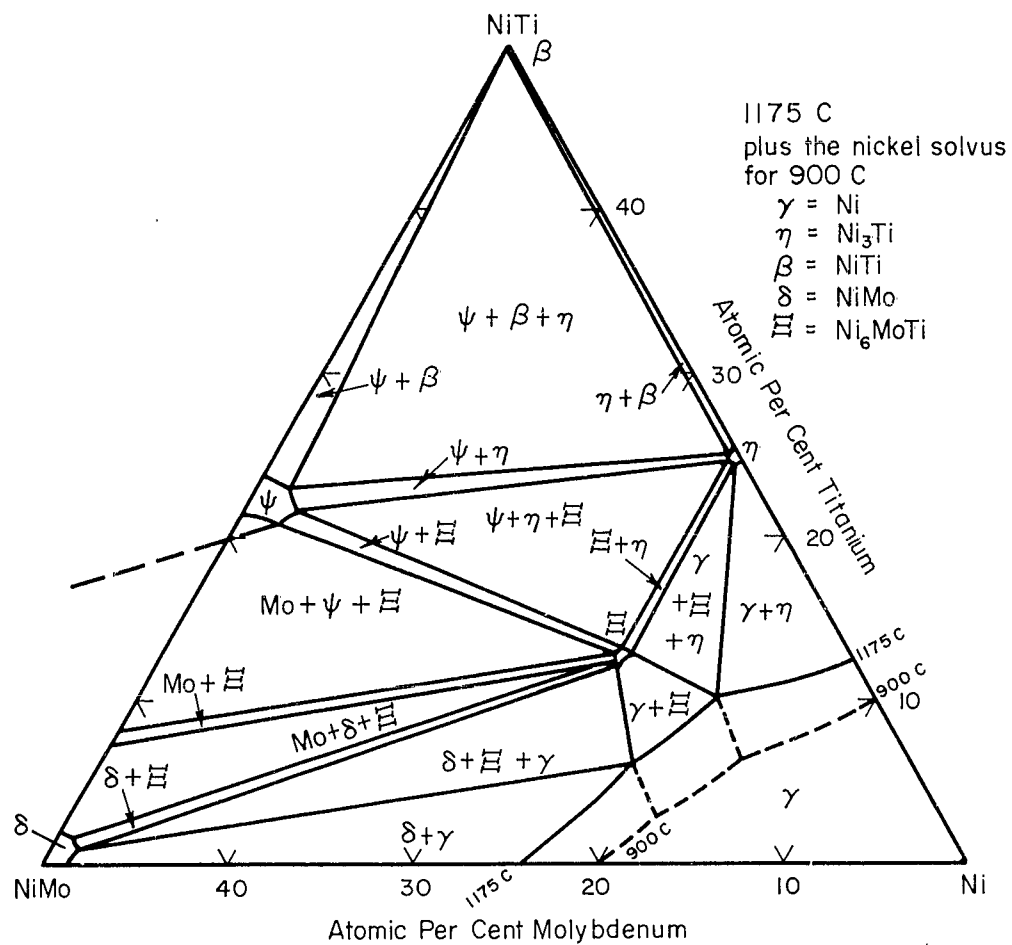


MOLYBDENUM-OXYGEN-TITANIUM SYSTEM (1500 C)⁽³¹⁴⁾

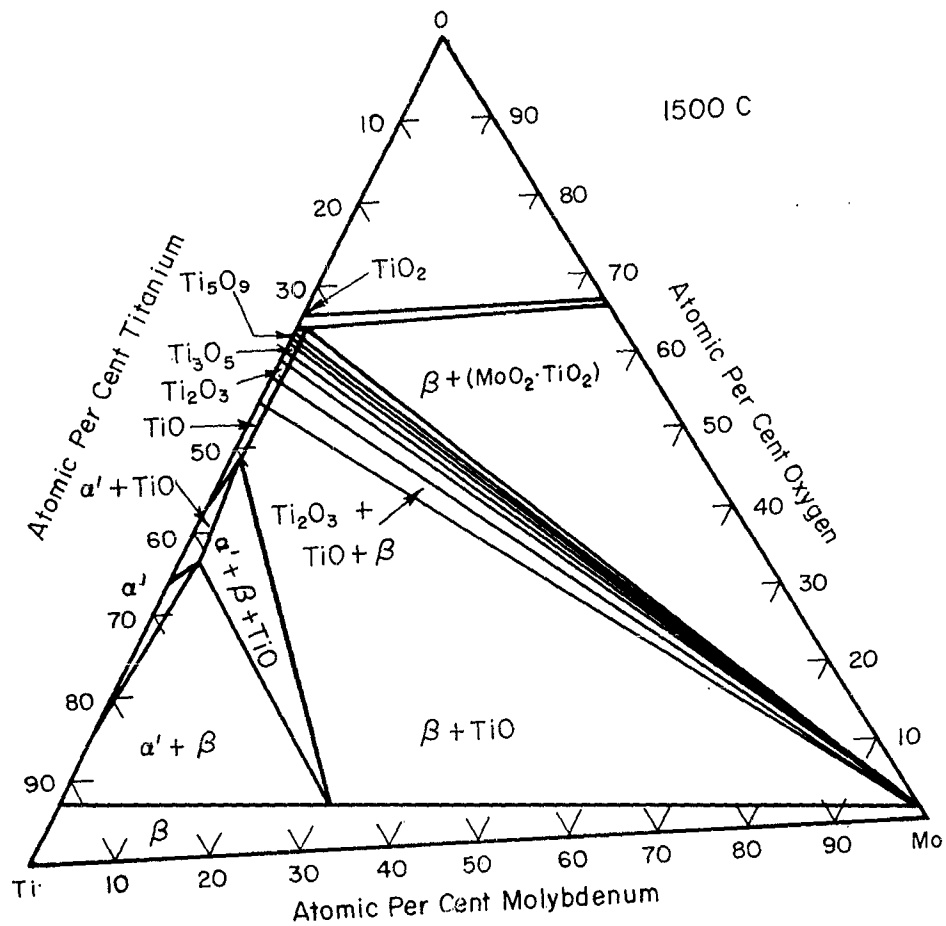


MOLYBDENUM-OXYGEN-ZIRCONIUM SYSTEM (1500 C)⁽³¹⁴⁾

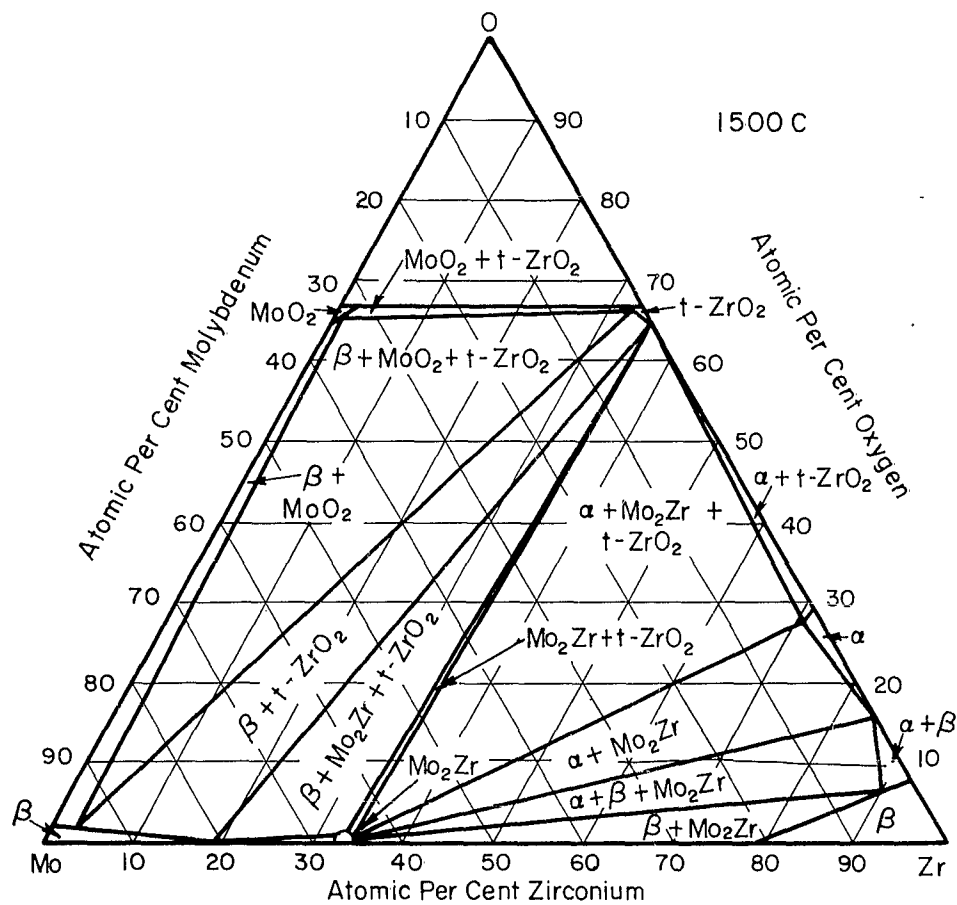


MOLYBDENUM-SILICON-VANADIUM SYSTEM (800 C)⁽³⁰³⁾

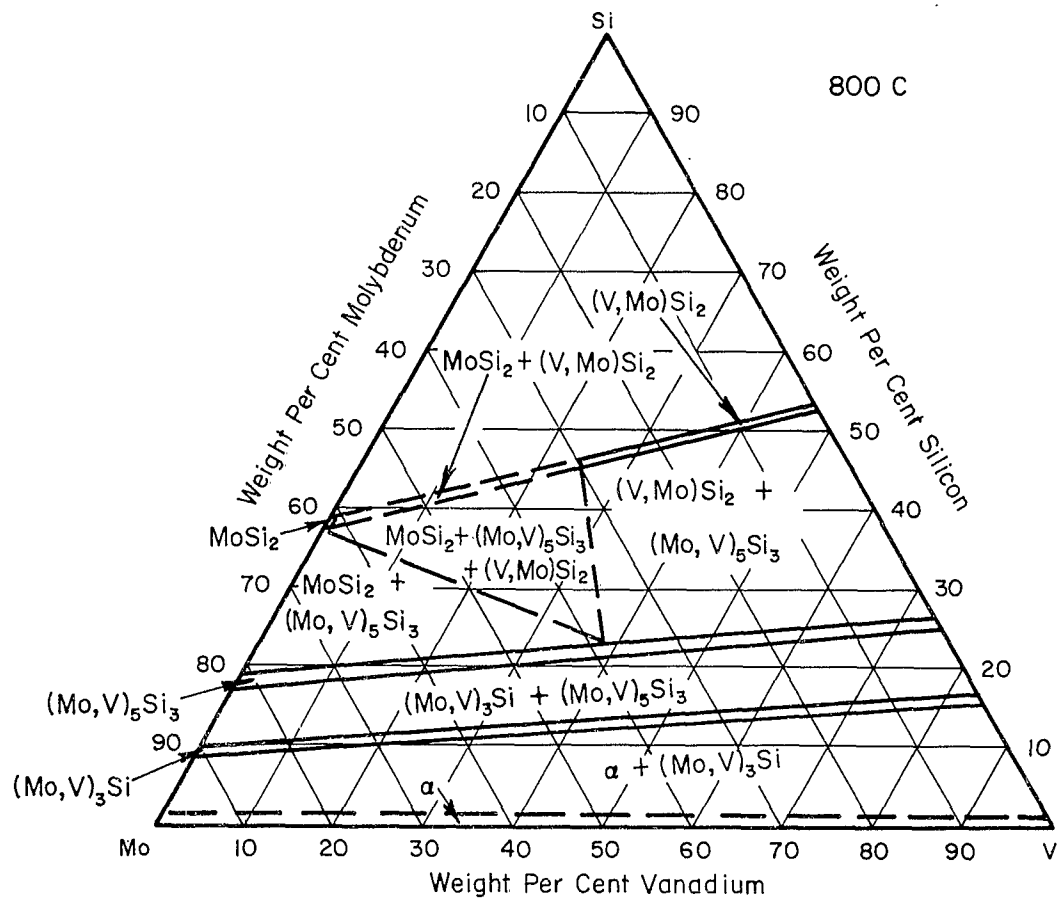


MOLYBDENUM-TITANIUM-VANADIUM SYSTEM (ROOM TEMPERATURE)⁽²⁸⁷⁾

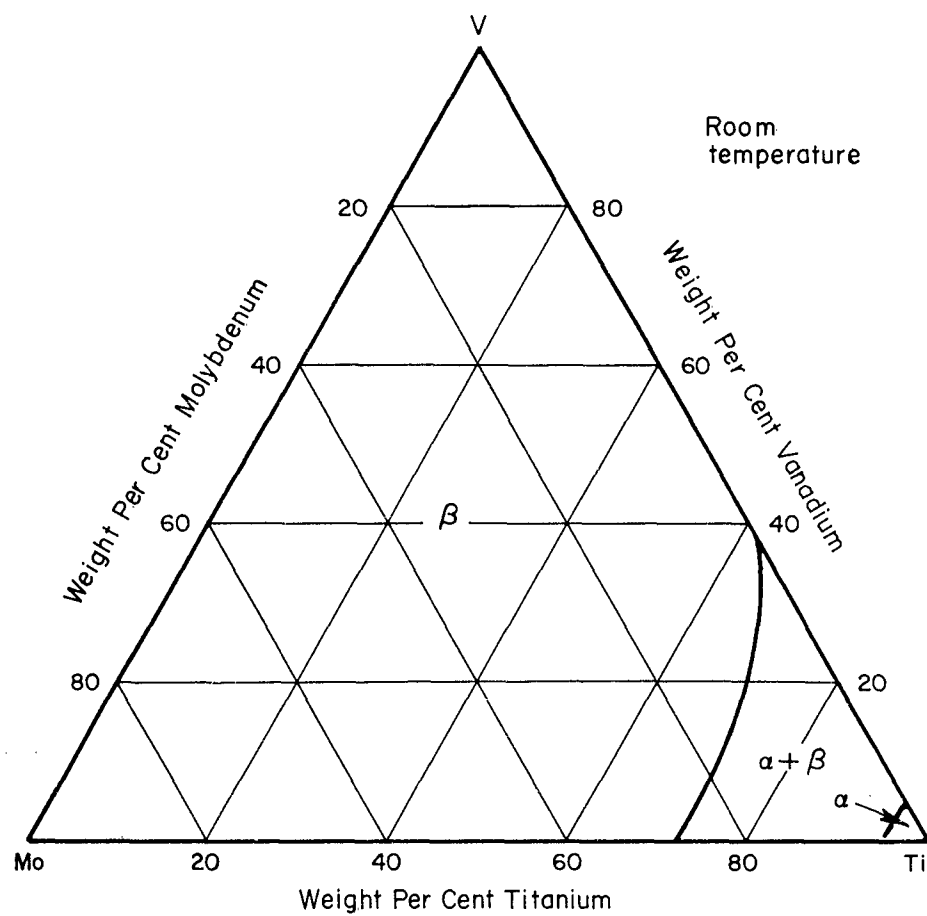


MOLYBDENUM-TITANIUM-ZIRCONIUM SYSTEM (1500 C)(314)

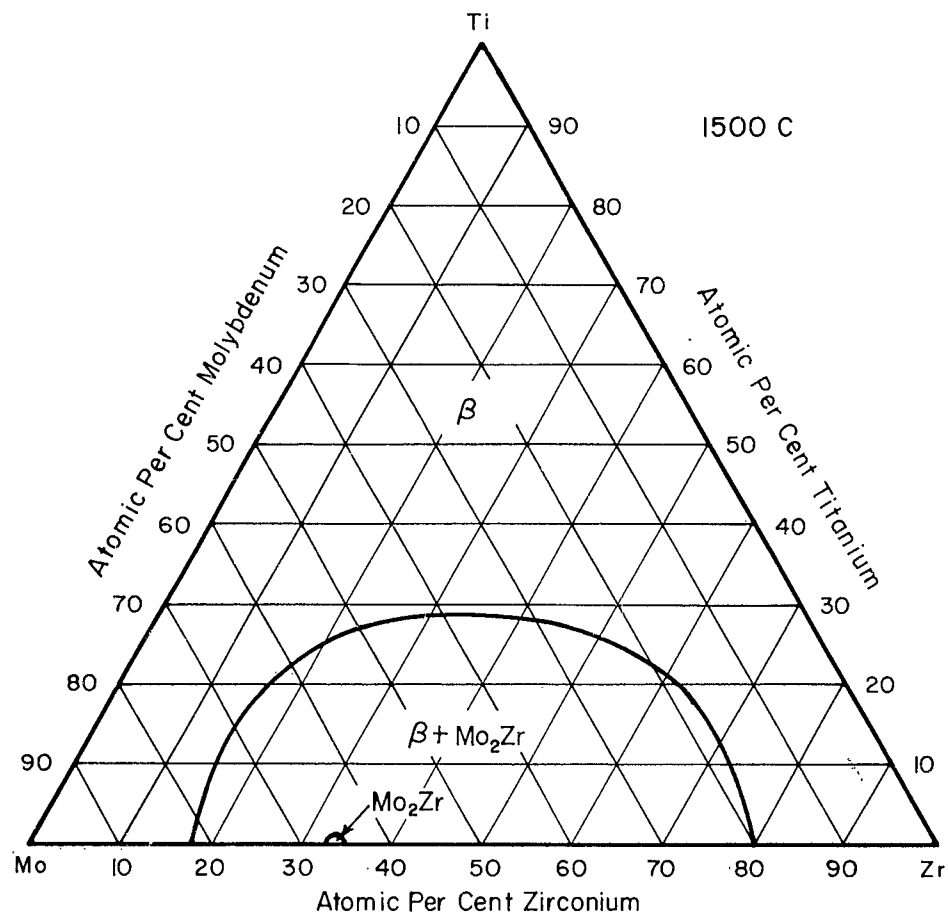

MOLYBDENUM-TUNGSTEN-CHROMIUM SYSTEM (1800 C)(288)

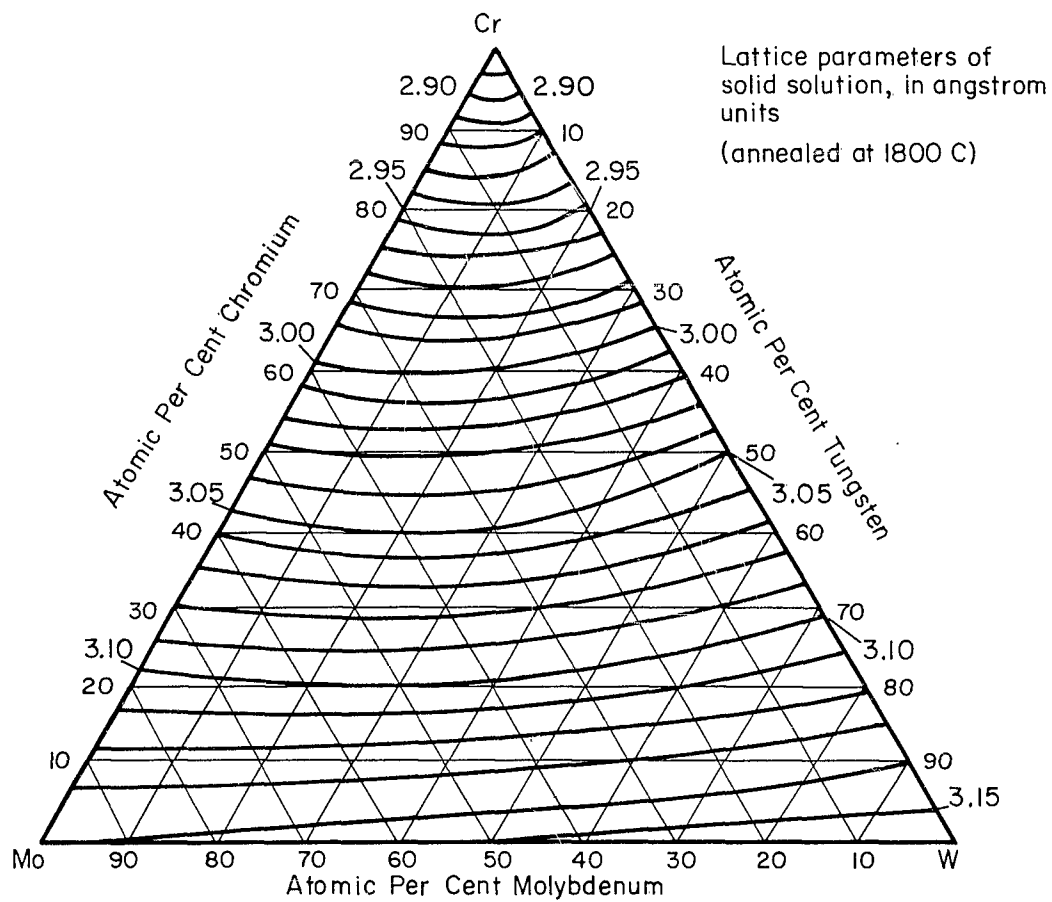


MOLYBDENUM-TUNGSTEN-SILICON SYSTEM (1900 C)⁽²⁹⁴⁾

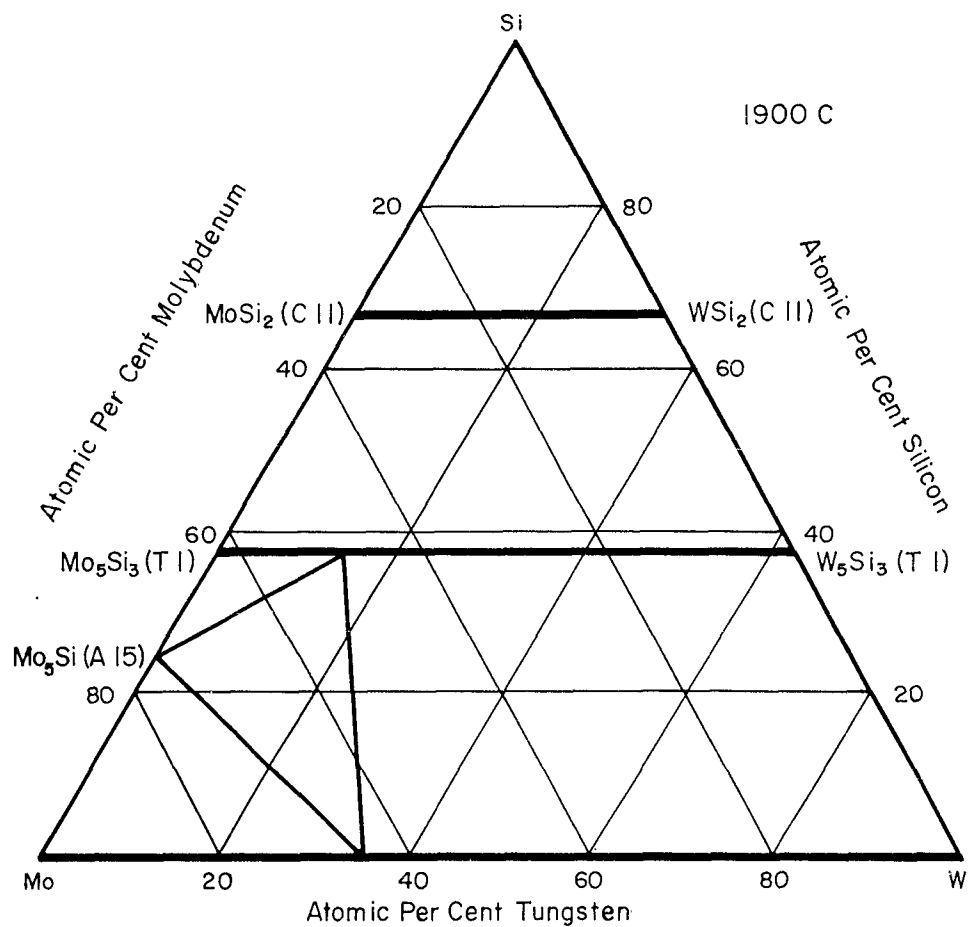


1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
66
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
84




MOLYBDENUM-URANIUM-VANADIUM SYSTEM (600 C)(308)

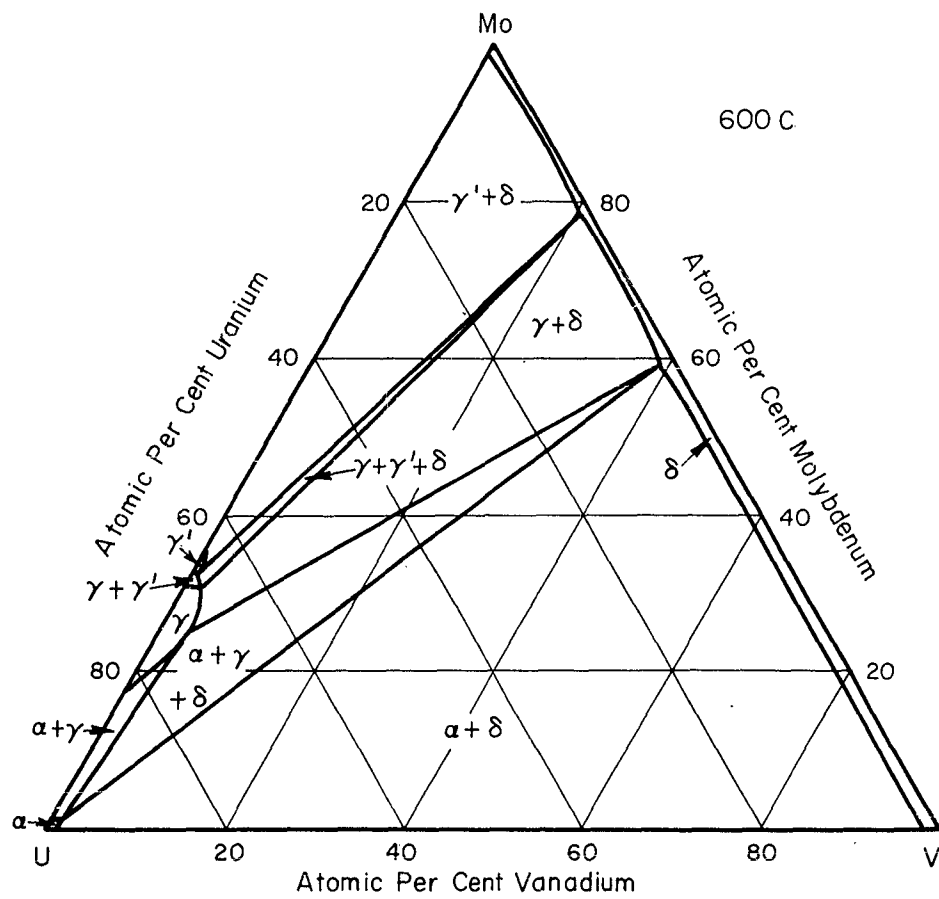


MOLYBDENUM-URANIUM-VANADIUM SYSTEM (1000 C)⁽³⁰⁸⁾

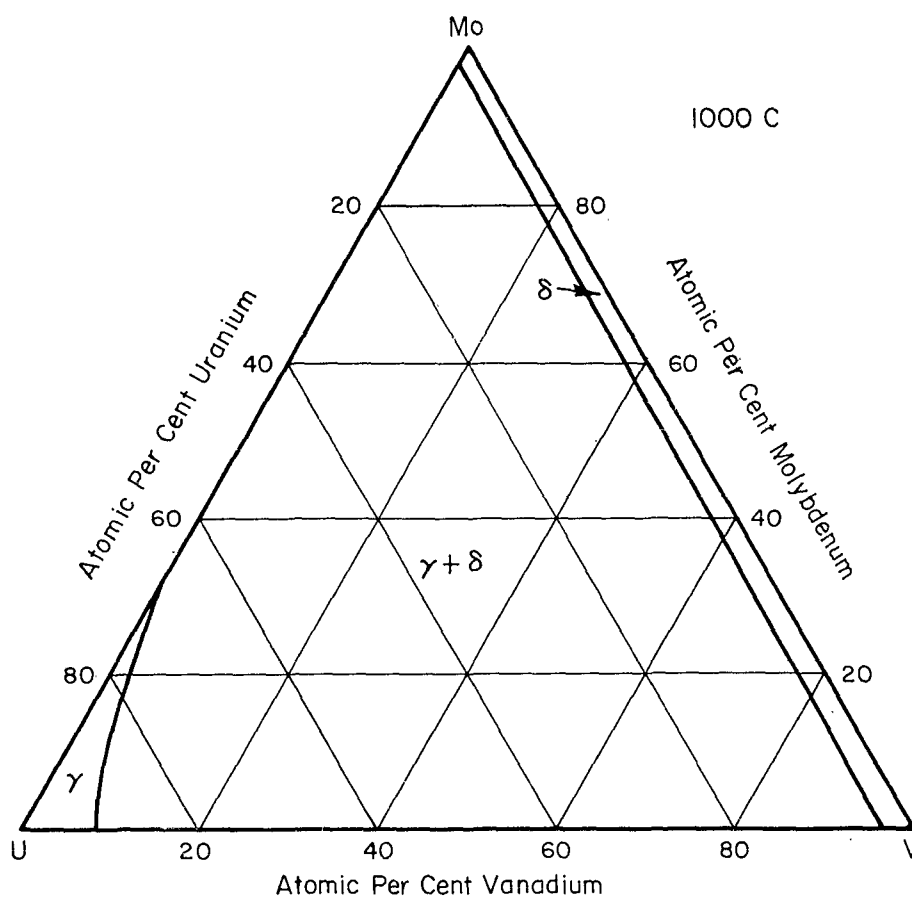


MOLYBDENUM-URANIUM-ZIRCONIUM SYSTEM (1000 C)⁽²⁸⁰⁾

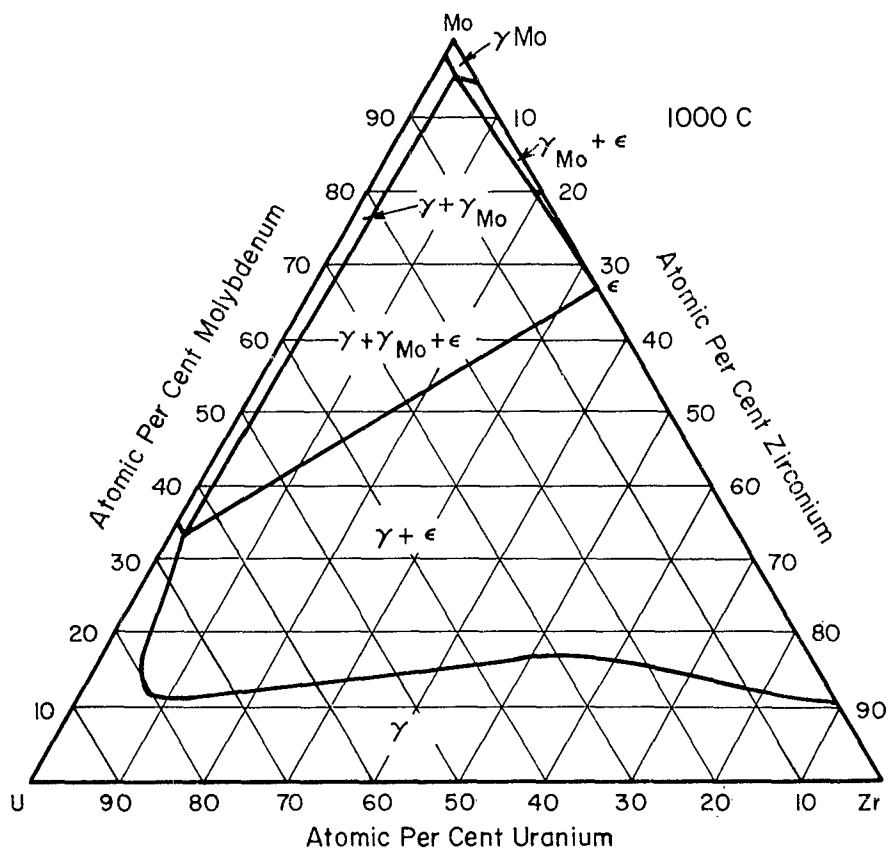

TANTALUM-ALUMINUM-SILICON SYSTEM (1400 C)(266)

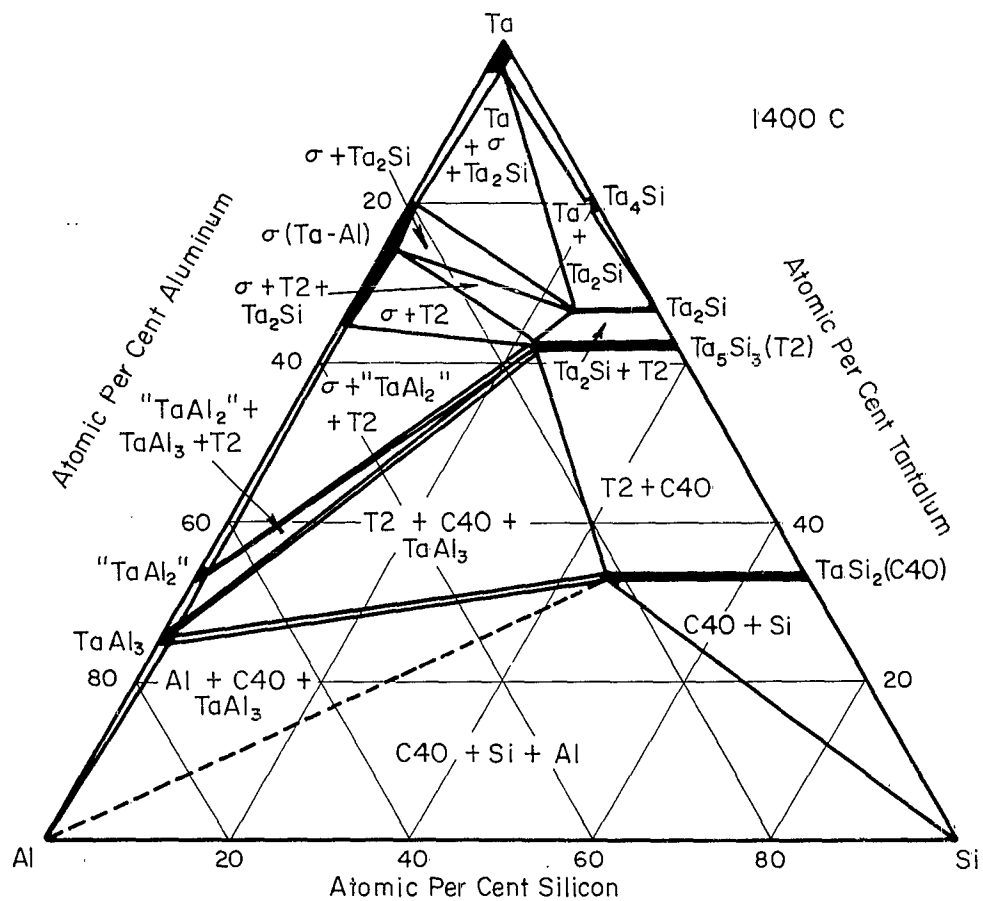


TANTALUM-BORON-NICKEL SYSTEM (TaB_2 -Ni)

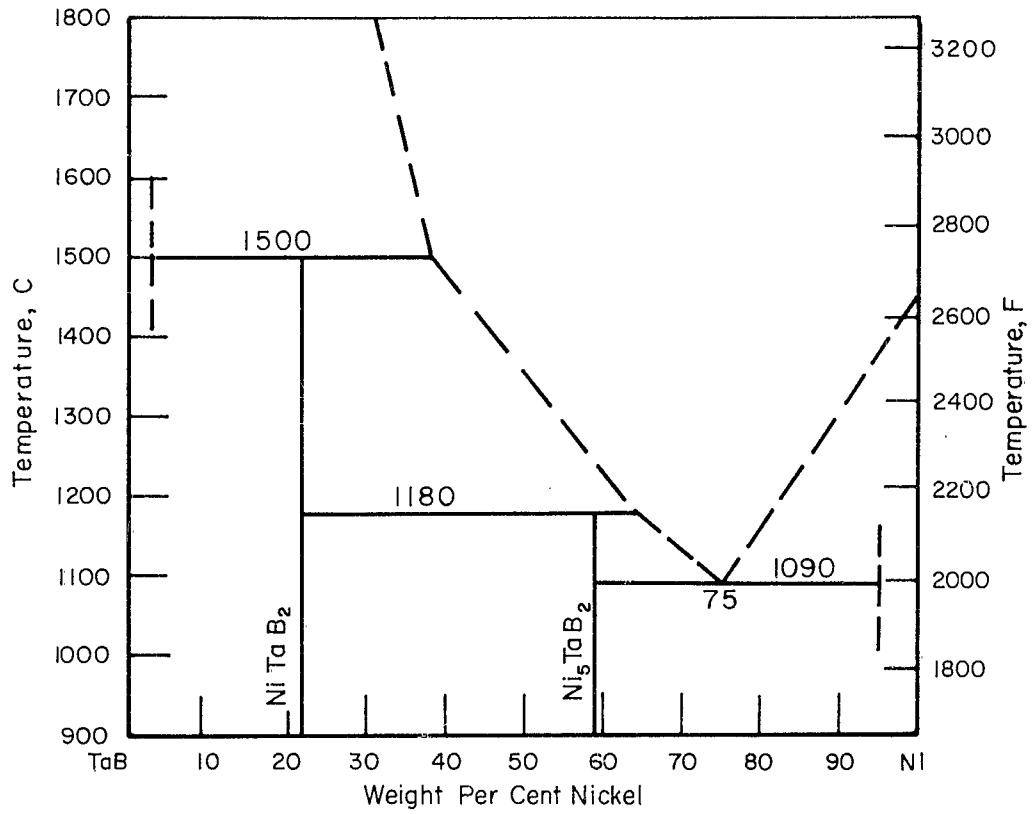


Ni_5TaB_2 has a face-centered cubic structure with $a = 10.56 \text{ \AA}$.⁽²⁸⁹⁾ The structure of NiTaB_2 was not identified.


TANTALUM CARBIDE-HAFNIUM CARBIDE-URANIUM CARBIDE SYSTEM (2050 C)⁽²⁷¹⁾

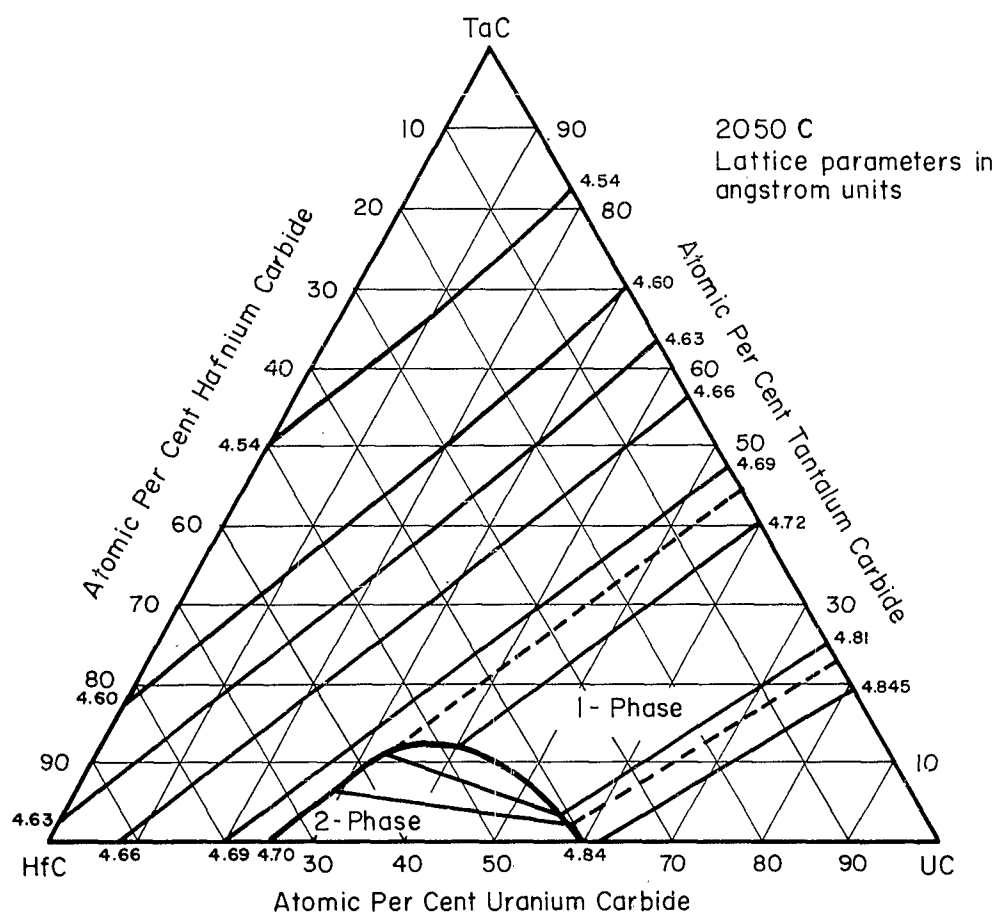


TANTALUM CARBIDE-HAFNIUM CARBIDE-VANADIUM CARBIDE SYSTEM (2050 C)⁽²⁷¹⁾

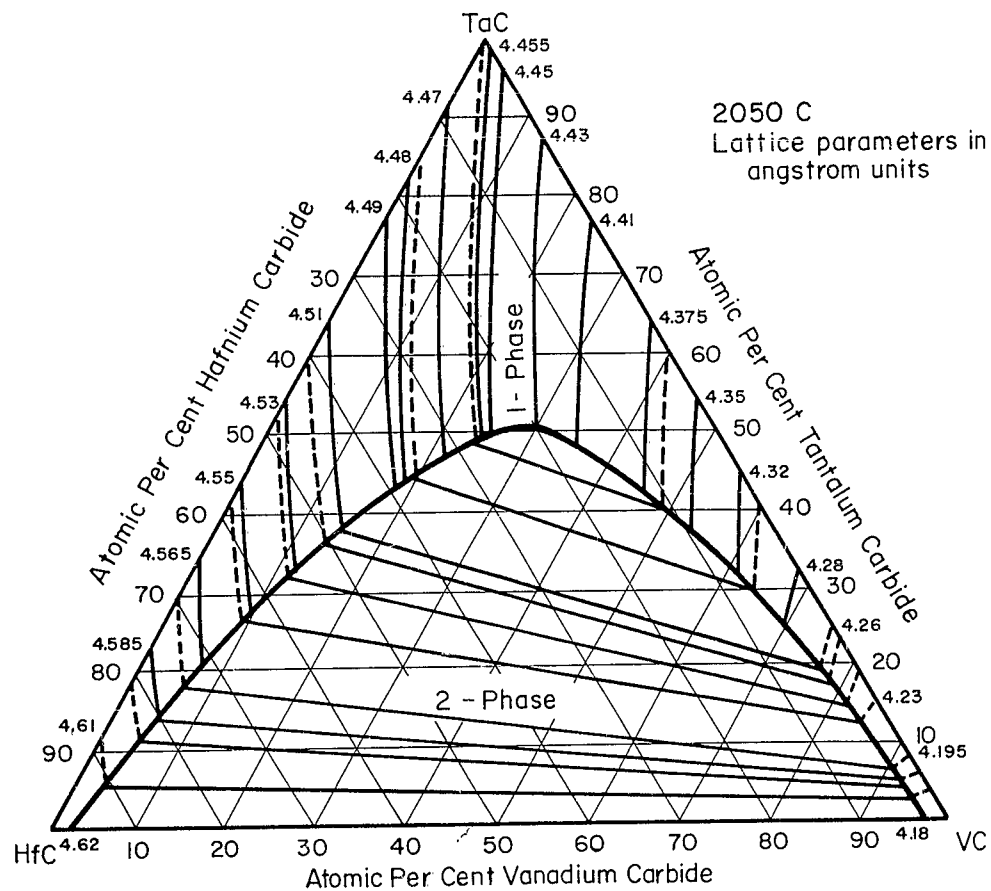


TANTALUM-CARBON-URANIUM SYSTEM (1700 C)⁽²⁷²⁾

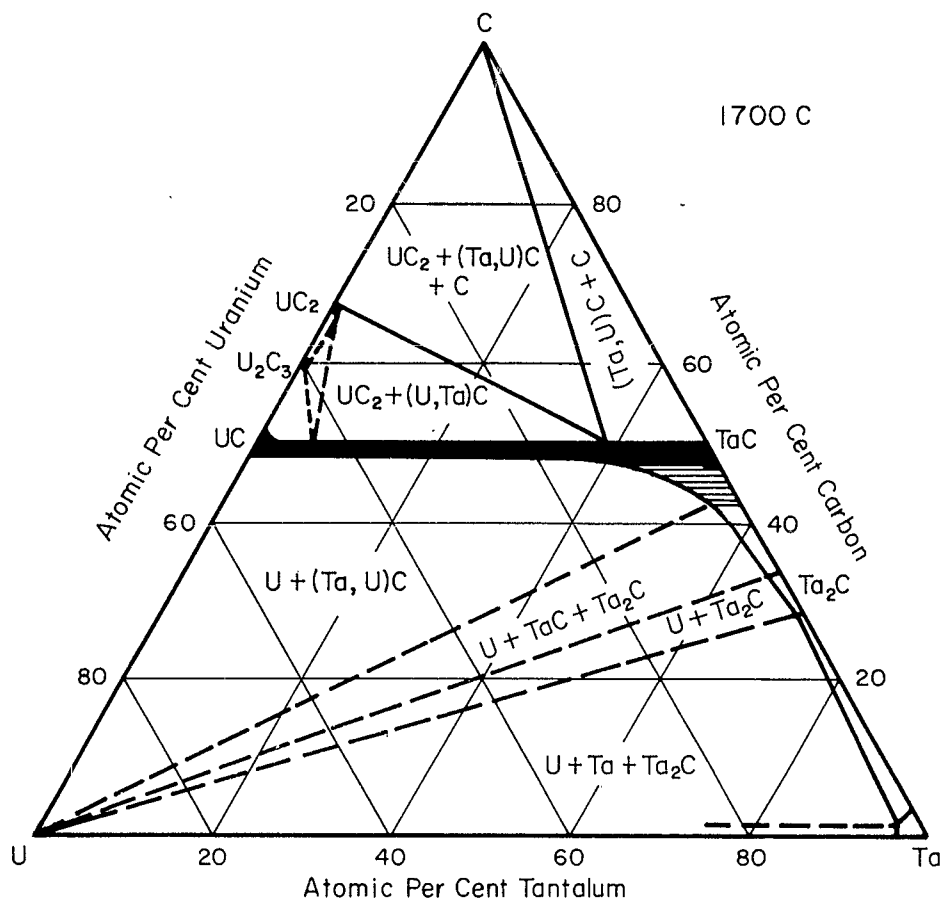


TANTALUM-CHROMIUM-NICKEL SYSTEM (SOLIDUS TEMPERATURE)⁽³²⁰⁾

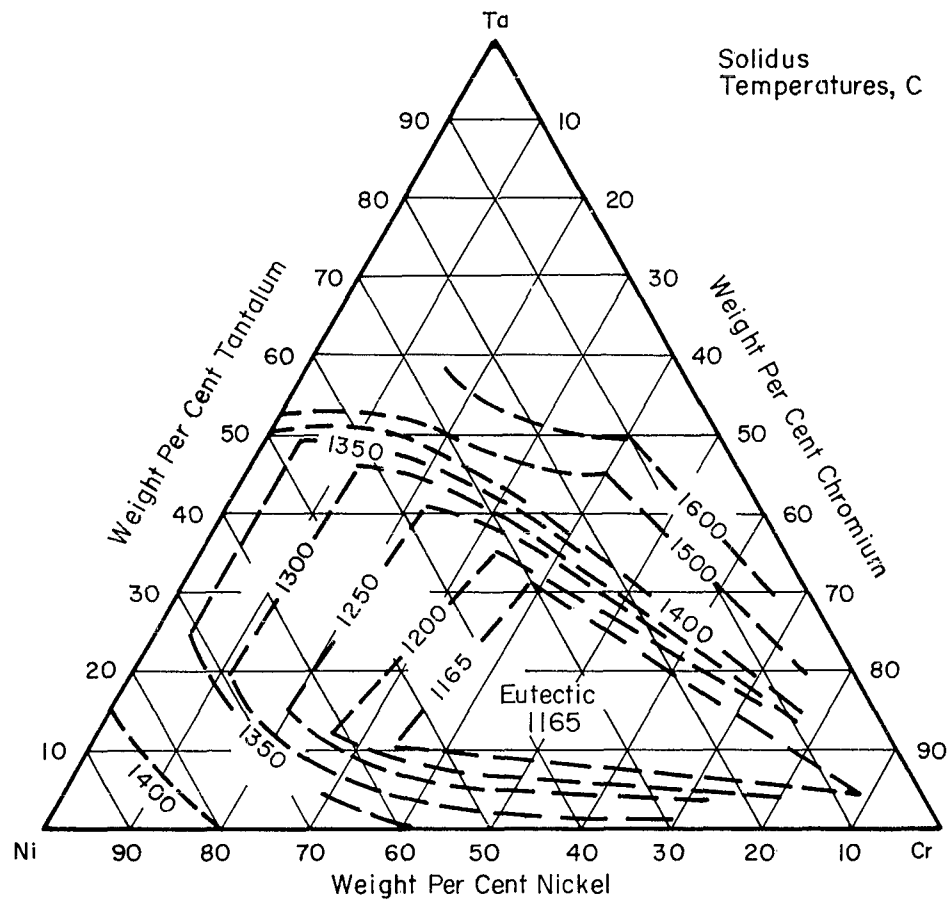


TANTALUM-COBALT-IRON SYSTEM (20 C)(290)

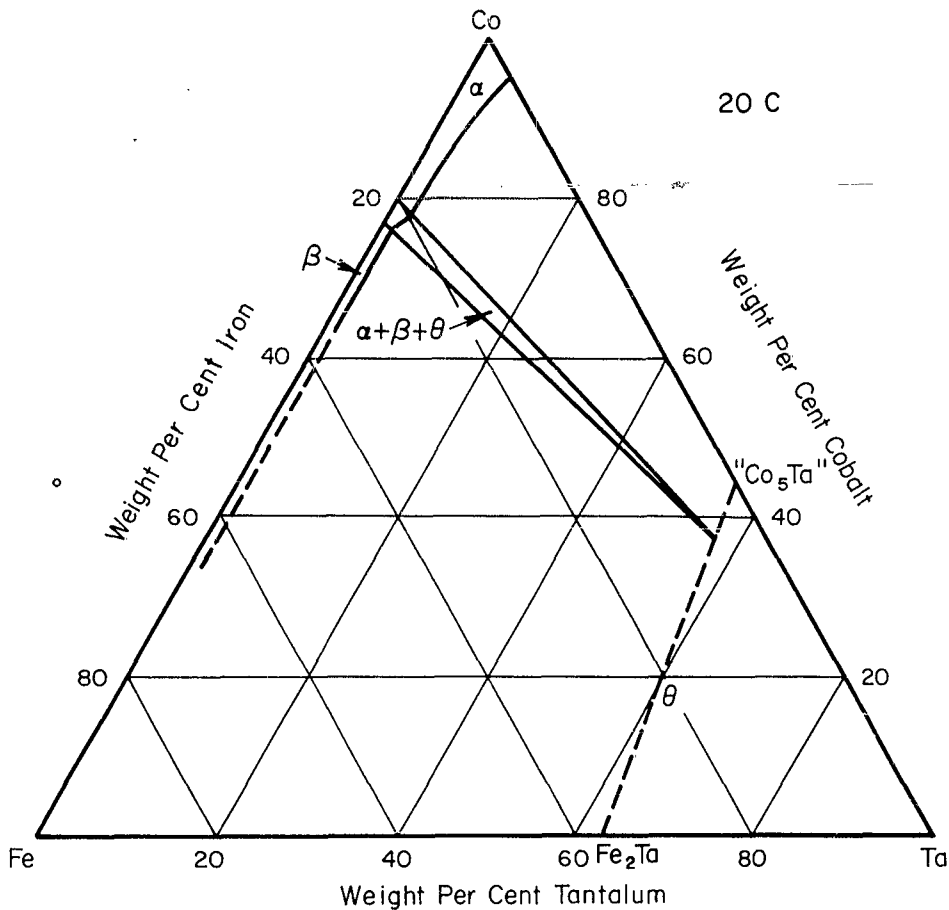


TANTALUM-COBALT-IRON SYSTEM (1390 C)(290)

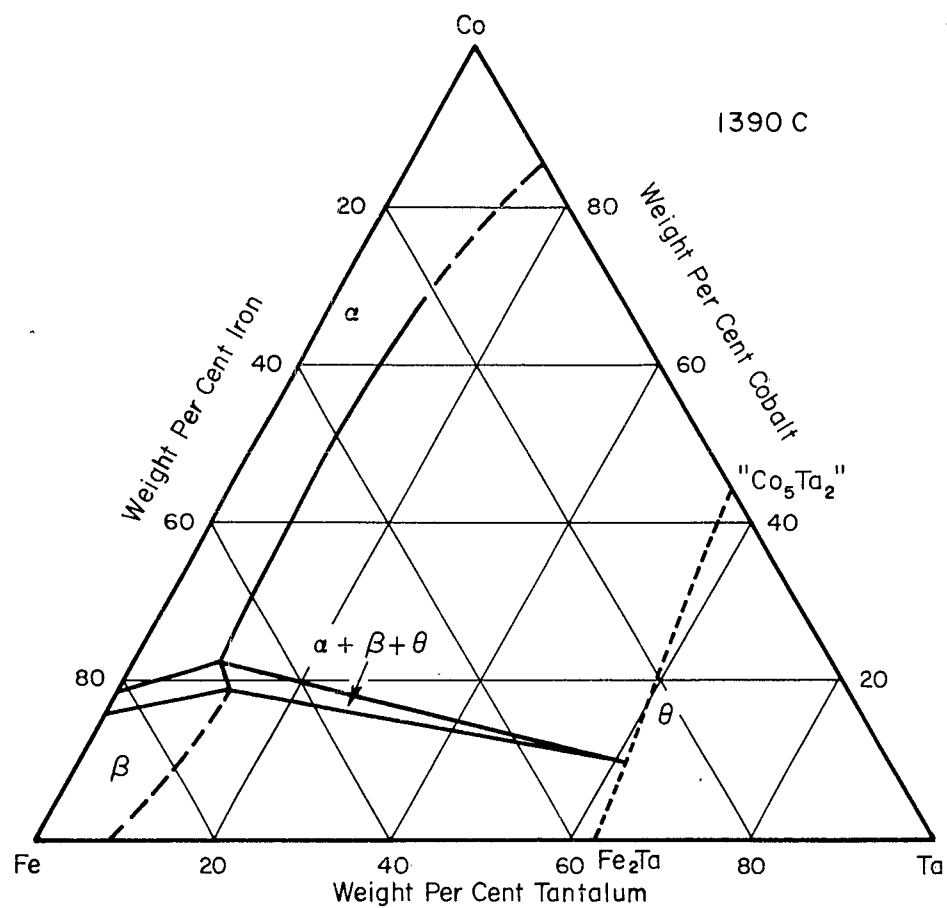


TANTALUM-SILICON-TITANIUM SYSTEM (TaSi_2 - TiSi_2)⁽³¹⁶⁾

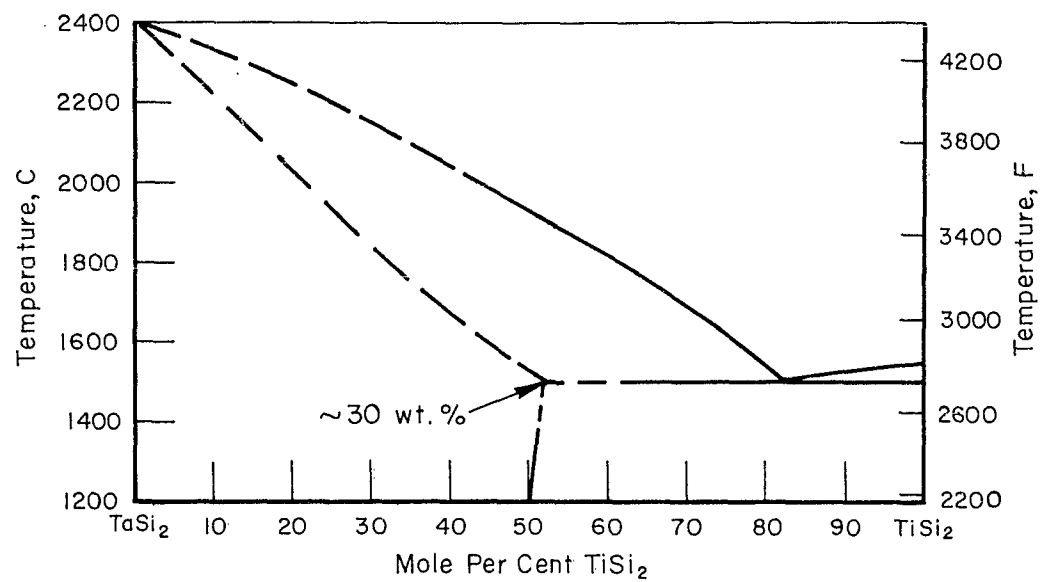


TANTALUM-SILICON-VANADIUM SYSTEM (SCHEMATIC)⁽³¹⁵⁾

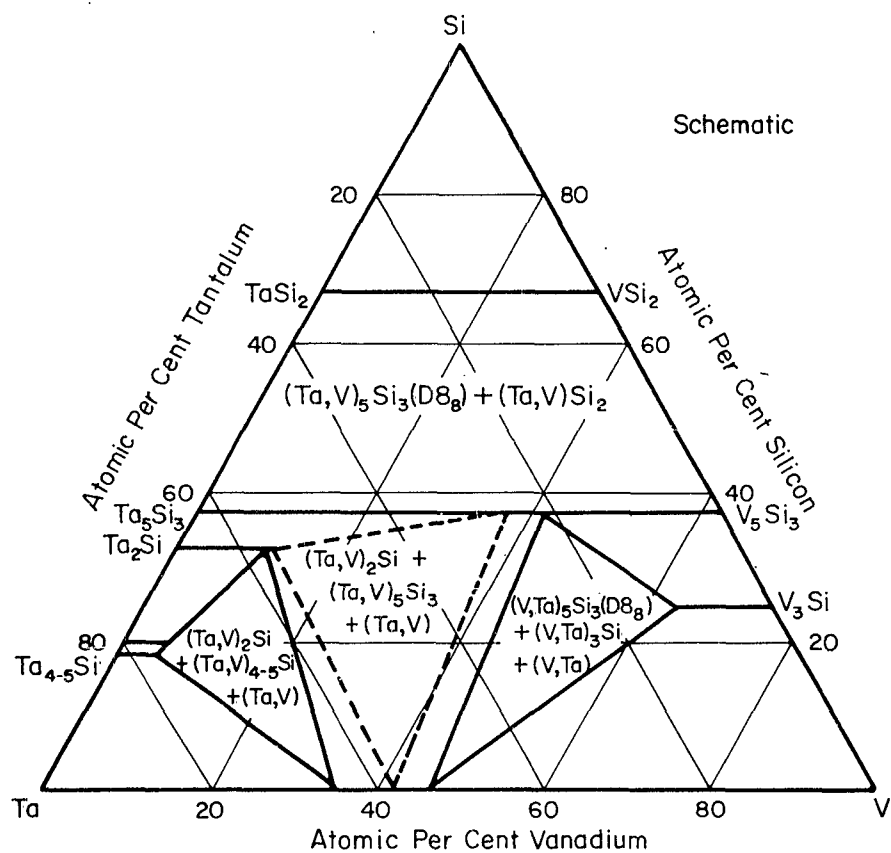


TANTALUM-TUNGSTEN-SILICON SYSTEM (TaSi_2 - WSi_2)(316)

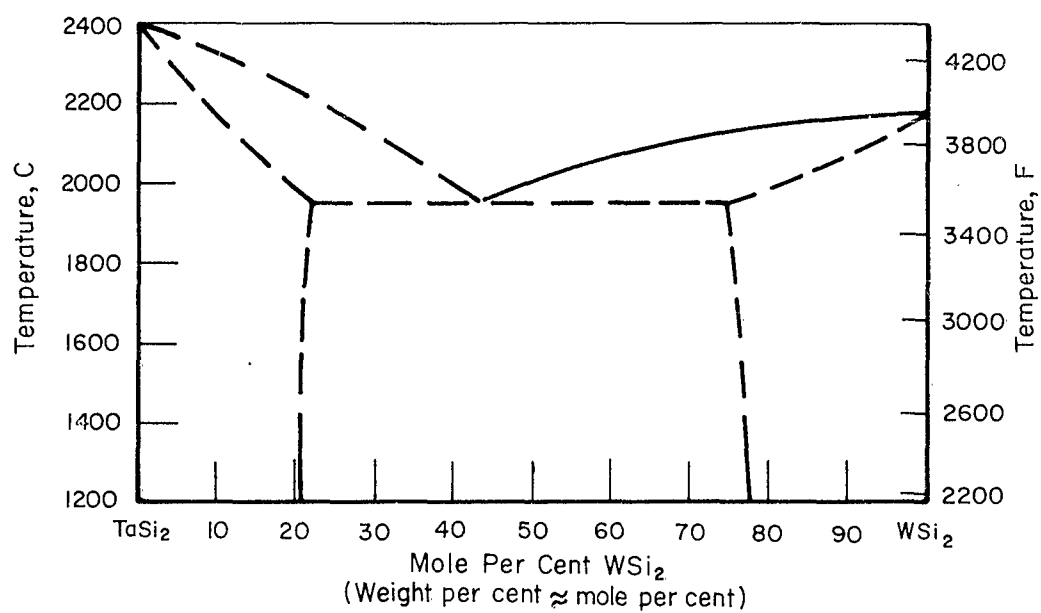


TUNGSTEN-ALUMINUM-NICKEL SYSTEM (800 C)(302)

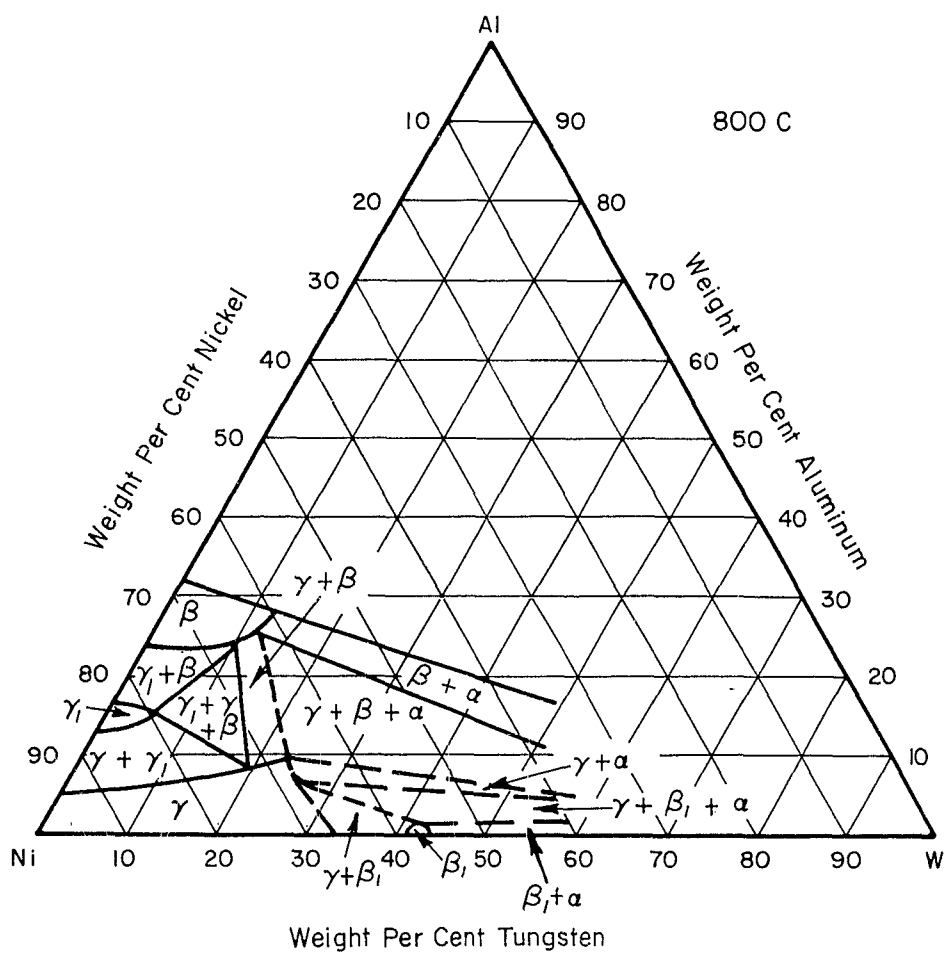


TUNGSTEN-ALUMINUM-NICKEL SYSTEM (1200 C)⁽³⁰²⁾

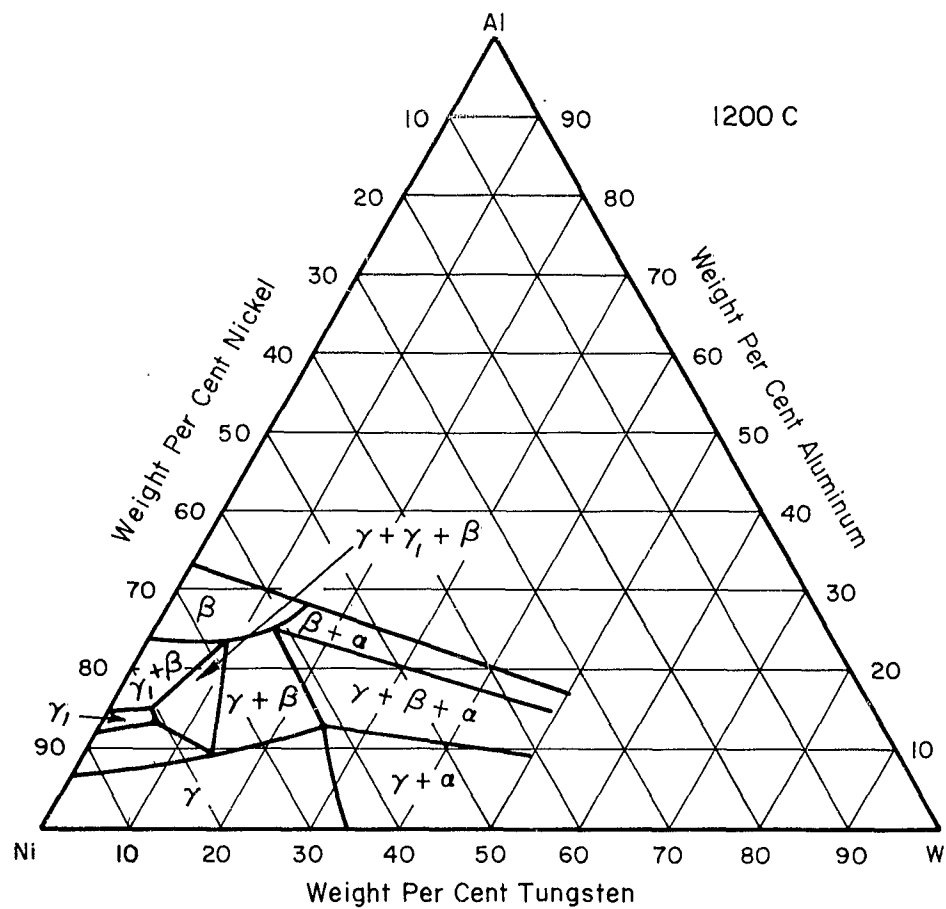

Atomic Per Cent Aluminum




TUNGSTEN-BORON-THORIUM SYSTEM (1800 C)⁽²⁹¹⁾

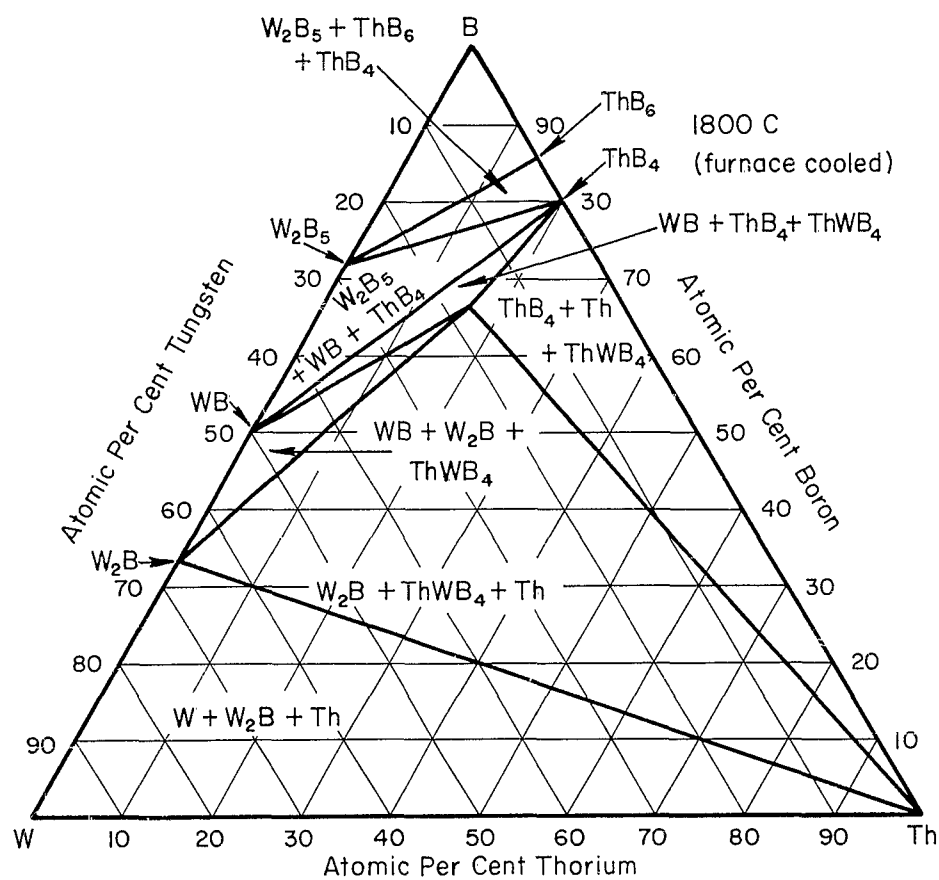


A ternary compound was found with a probable composition ThWB_4 . The compound is monoclinic with $a = 12.25 \text{ \AA}$, $b = 3.75 \text{ \AA}$, $c = 6.14 \text{ \AA}$, and $\beta = 104.1^\circ$.⁽²⁹¹⁾


TUNGSTEN-CARBON-THORIUM SYSTEM (1500 C)⁽²⁹²⁾

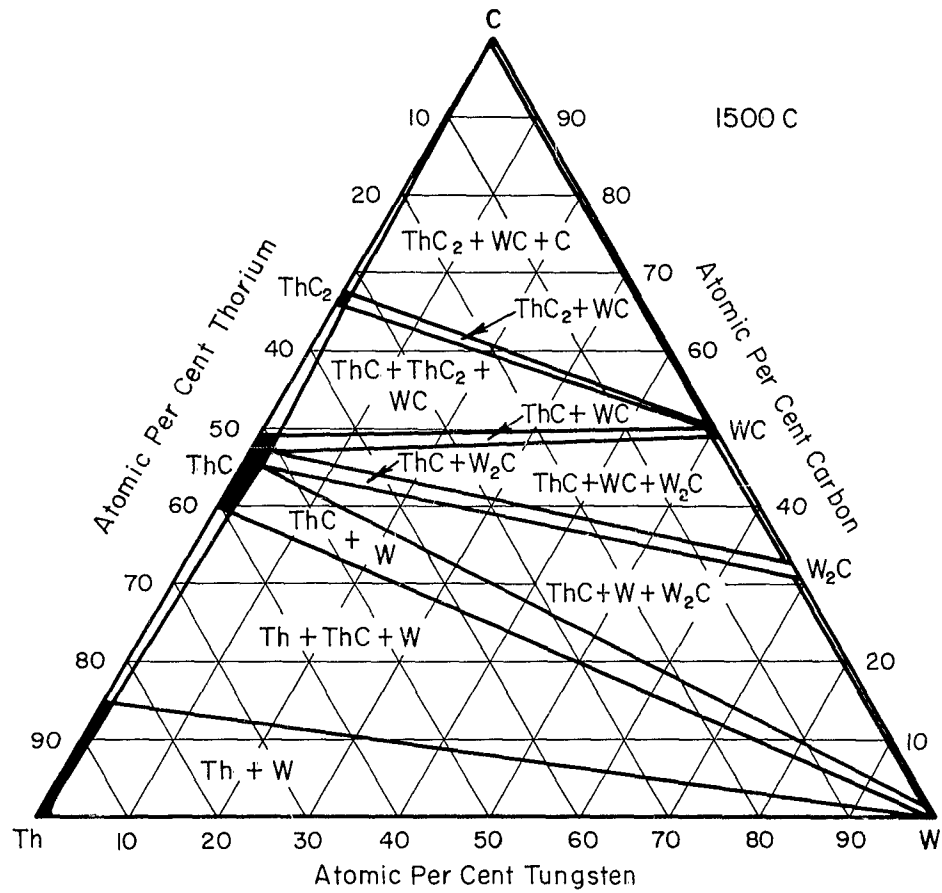


TUNGSTEN-CARBON-URANIUM SYSTEM (1000 AND 1500 C)(292)

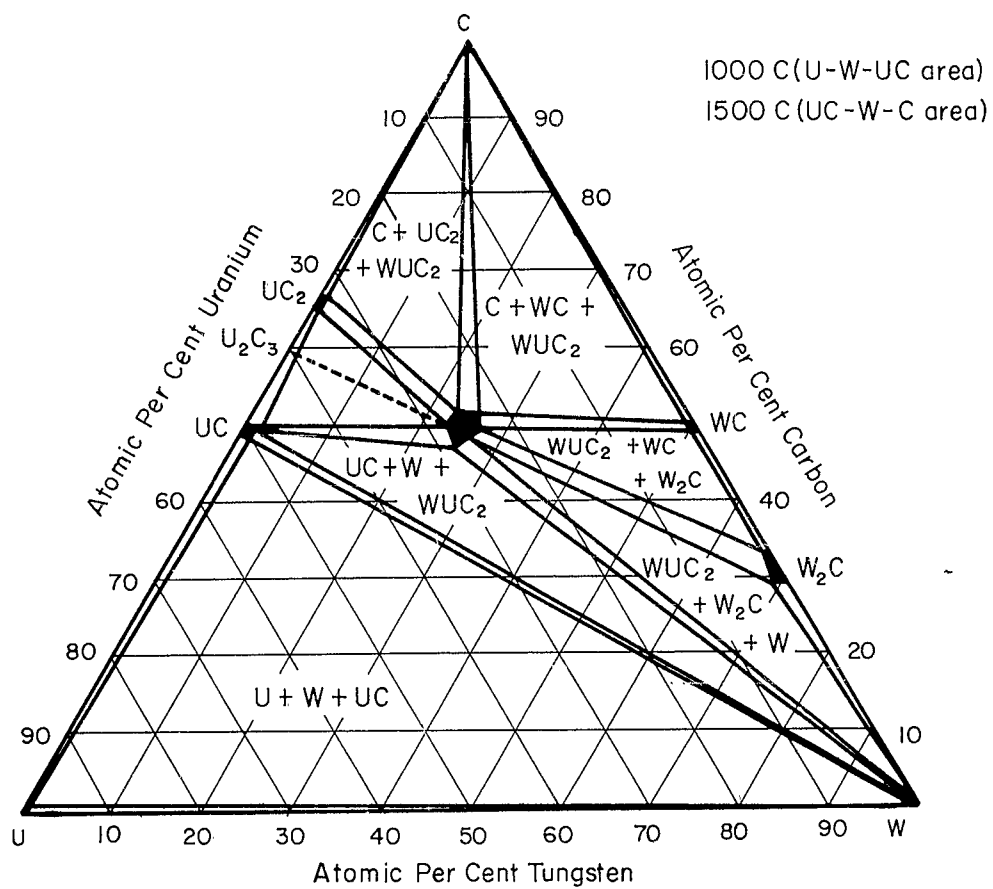

TUNGSTEN-CHROMIUM-COBALT SYSTEM (ROOM TEMPERATURE)⁽²⁹³⁾

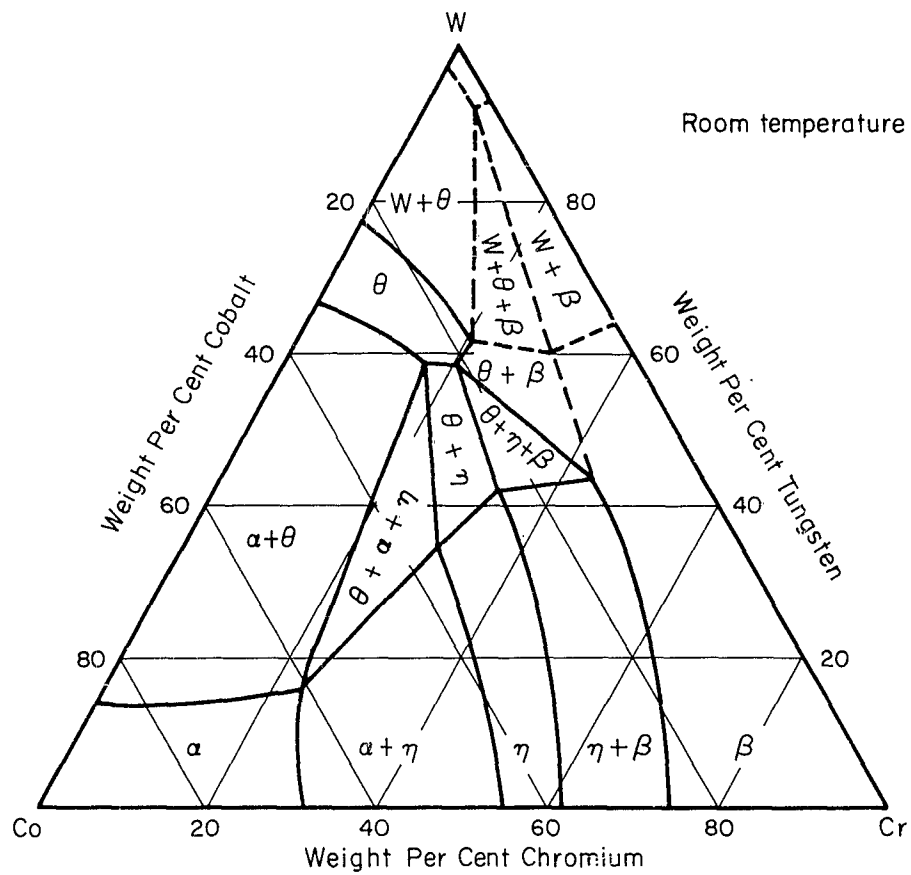


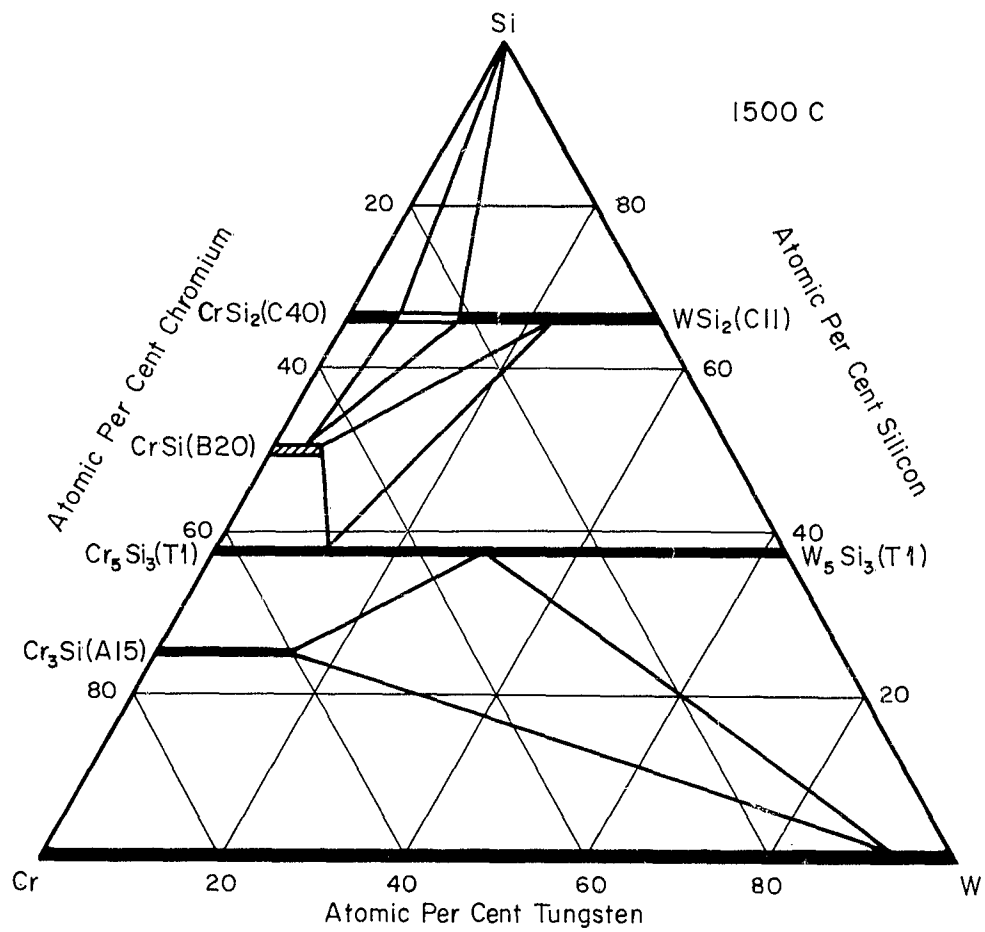TUNGSTEN-CHROMIUM-SILICON SYSTEM (1500 C)⁽²⁹⁴⁾


4




TUNGSTEN-COBALT-IRON SYSTEM (1400 C)⁽²⁹⁵⁾

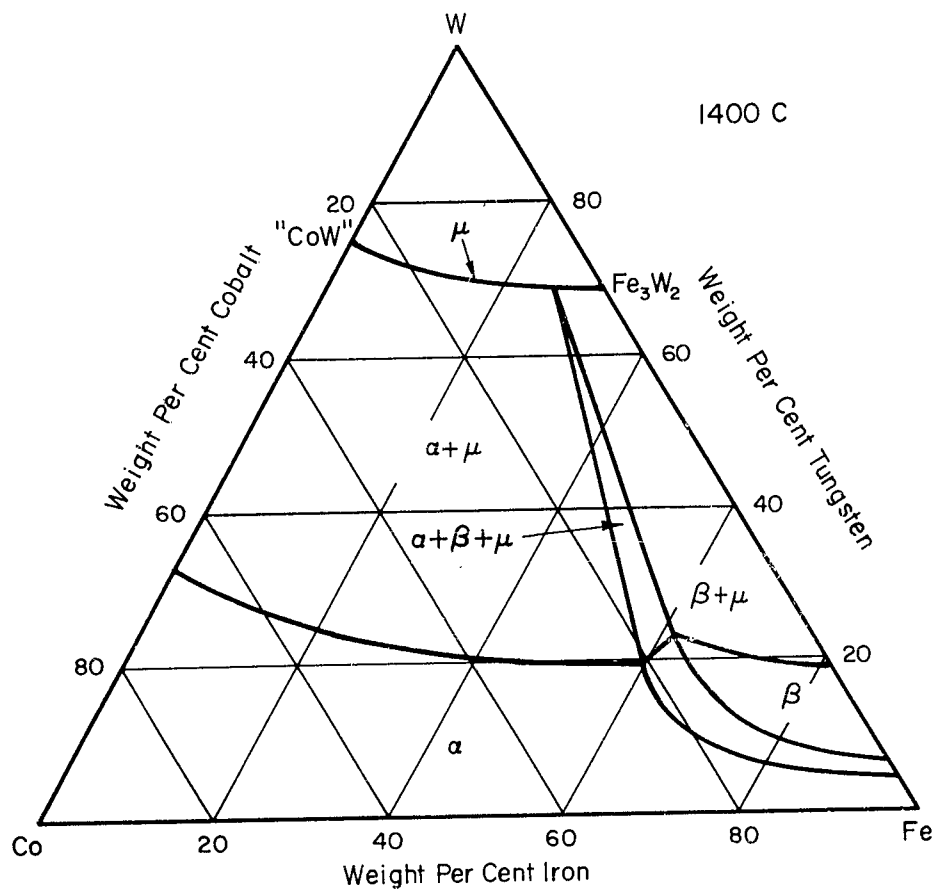


TUNGSTEN-GERMANIUM-SILICON SYSTEM (1000 C)⁽²⁹⁷⁾

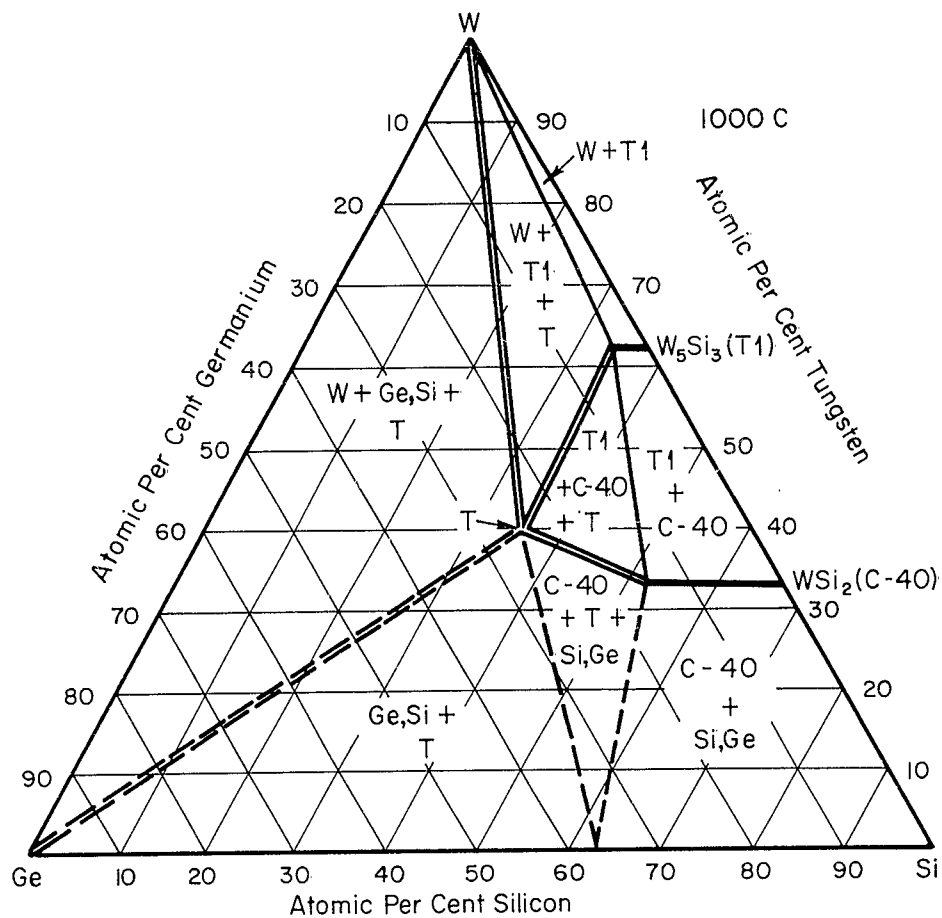

TUNGSTEN-IRON-SULFUR SYSTEM (ROOM TEMPERATURE)⁽²⁹⁶⁾

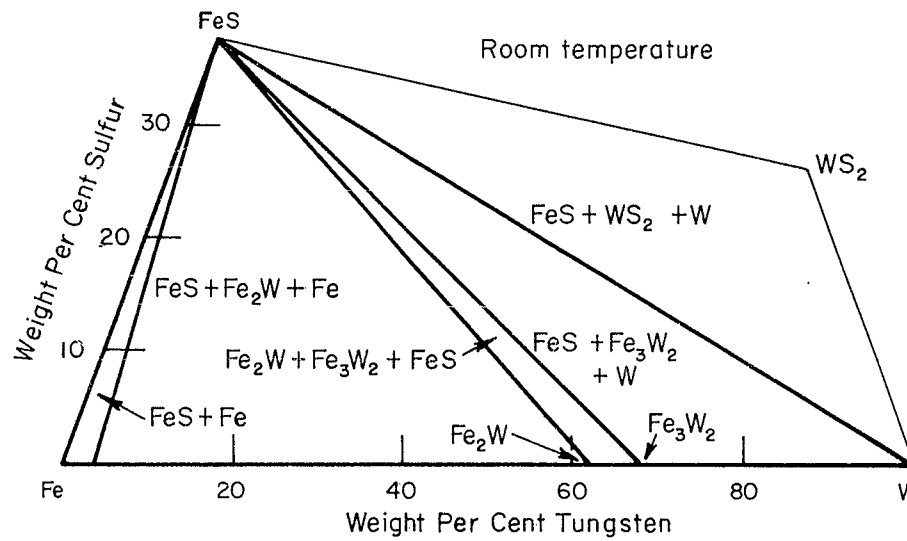

TUNGSTEN-SILICON-TITANIUM SYSTEM (TiSi_2 - WSi_2 SCHEMATIC)(316)

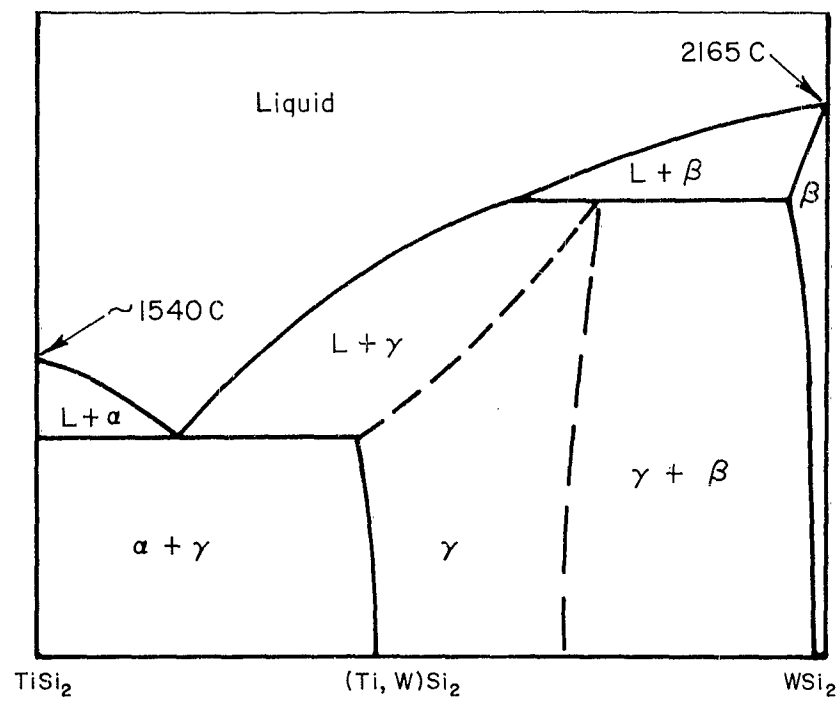

Schematic Diagram

BIBLIOGRAPHY

- (234) Baron, V. V., and Savitskiy, Ye. M., "Structure and Properties of Nb-Al Alloys", Zhur. Neorg. Khimii, 6 (1), 182-5 (1961).
- (235) Nedumov, N. A., and Rabezova, V. I., "Alloys of the Nb-Al System", Izvest. Akad. Nauk S.S.S.R., Otdel. Tekh. Nauk, Met. i Topliva, No. 4, 68-70 (1961).
- (236) Gupta, K. P., "Sigma Phases with Aluminum", Trans. AIME, 221, 1047-1049 (1961).
- (237) Pleasance, R. J., "The Solubilities of Niobium, Cesium, and Strontium in Liquid Bismuth", J. Inst. Metals, 88, 45-46 (1959-60).
- (238) Storms, E. K., and Krikorian, N. H., "The Niobium-Niobium Carbide System", J. Physical Chem., 64, 1471-1477 (October, 1960).
- (239) Kimura, H., and Sasaki, Y., "Phase Diagram of the Niobium-Carbon System", Trans. Japan Inst. Metals, 2, 98-104 (1961).
- (240) Seebold, R. E., and Birks, L. S., "Elevated Temperature Diffusion in the Systems Nb-Pt, Nb-Se, Nb-Zn, Nb-Co, Ni-Ta, and Fe-Mo, J. Nuclear Materials, 3, 260-66 (1961).
- (241) Povov, I. A., and Shiryayeva, N. V., "State Diagram of the System Nb-Cu, Zhur. Neorg. Khimii, 6 (10), 2334-2340 (1961).
- (242) Schubert, K., Anantharaman, T. R., et al., "Einige strukturelle Ergebnisse an metallischen Phasen (6)", Naturwiss., 47, 512 (1960).
- (243) Elliott, R. P., and Komjathy, S., "Columbium-Nitrogen System", paper presented at the Columbium Metallurgy Symposium, Lake George, New York, June 10, 1960.
- (244) Savitskiy, Ye. M., Baron, V. V., and Khotinskaya, A. N., "Composition Diagram of the System Nb-Pd", Zhur. Neorg. Khimii, 6 (11), p 2603-2605 (1961).
- (245) Kimura, H., and Akira, I., "The Platinum-Niobium System", Nippon Kinzoku Gakkari, 25, 88-91 (January, 1961).
- (246) Novoselova, A. V., Grigoryan, L. A., and Simanov, Yu. P., "The Niobium-Tellurium System", Dokl. Akad. Nauk S.S.S.R., 135, 864-67 (1960).
- (247) Lundin, C. E., and Klodt, D. T., presented at ASM-AEC Joint Symposium on the Rare Earths and Related Metals, Chicago, Illinois, November, 1959.
- (248) Taylor, A., preliminary work under AF Contract AF 33(616)-8315.
- (249) Lundin, C. E., and Klodt, D. T., "The Alloy Systems of the Group V-A Metals with Yttrium", J. Inst. Metals, 90, 341-347 (May, 1962).

- (250) Taylor, A., Doyle, N., and Kagle, B., "Refractory Metal Constitution Diagrams - Part II", Westinghouse Research Laboratories, Air Force Contract AF 33(616)-7157, March, 1962.
- (251) Anderson, E., and Hume-Rothery, W., "The Equilibrium Diagram of the System Molybdenum-Ruthenium", J. Less-Common Metals, 2 (6), 443-450 (1960).
- (252) Raub, E., Beeskow, H., and Menzel, D., "Tantalum-Gold Alloys", Z. Metallk., 52, 189-93 (1961).
- (253) Nevitt, M. V., and Downey, J. W., "Sigma Phases Containing Osmium and Iridium", J. Metals, 9, 1072 (1957).
- (254) Giessen, B., "Refractory Metal Constitution Diagrams - Part II", Massachusetts Institute of Technology, Air Force Contract AF 33(616)-7157, March, 1962.
- (255) Dwight, A. E., and Beck, P. A., "Close-Packed Ordered Structures in Binary AB₃ Alloys of Transition Elements", Trans. AIME, 215 (6), 976-979 (1959).
- (256) Gebhardt, E., Seghezzi, H. D., and Fromm, E., "Investigation of the Equilibrium in the System Tantalum-Nitrogen", Z. Metallk., 52, 464-76 (1961).
- (257) Browning, B. D., "Investigation of the Pt-Rich Portion of the Platinum-Tantalum Phase Diagram", Air Force Institute of Technology, August, 1961.
- (258) Pease, L. F., Brophy, J. H., and Wulff, J., "Refractory Metal Constitution Diagrams - Part II", Massachusetts Institute of Technology, Air Force Contract AF 33(616)-7157.
- (259) Goldschmidt, H. S., and Brand, J. A., "Investigation Into the Tungsten-Rich Regions of the Binary Systems Tungsten-Carbon, Tungsten-Boron and Tungsten-Beryllium", Air Force Contract No. AF 61(052)-306, 1959-1961.
- (260) Dolloff, R. T., and Sara, R. V., "Research Study to Determine the Phase Equilibrium Relations of Selected Carbides at High Temperatures", Research Laboratory National Carbon Company, Progress Report No. 7, May 1, 1961, to July 31, 1961.
- (261) Raub, E., and Walter, P., Festschrift aus Anlass des 100-jährigen Jubiläums der Firma W. C. Heraeus G.m.b.H., Hanau (1951), pp 124-146.
- (262) Rapperport, E. J., and Smith, M. F., "Refractory Metal Constitution Diagrams - Part II", Nuclear Metals, Inc., Air Force Contract AF 33(616)-7157, March, 1962.
- (263) Smithells, C. J., Tungsten, Chemical Publishing Company, New York (1953), p 266.
- (264) St. Pierre, G. R., Ebihara, W. T., Pool, M. J., and Speiser, R., "The Tungsten-Oxygen System", Trans. AIME, 224, 259-264 (April, 1962).

- (265) Tylkina, M. A., Polyakova, V. P., and Savitskiy, Ye. M., "State Diagram of the System Palladium-Tungsten", Zhur. Neorg. Khimii, 6 (6), 1471-1473 (1961).
- (266) Nowotny, H., Brukl, C., and Benesovsky, F., "Investigation of the Tantalum-Aluminum-Silicon and Tungsten-Aluminum-Silicon Systems", Mh. Chemie, 92 (1), 116-127 (1961).
- (267) Edshammar, L., and Holmberg, B., "The σ -Phase Ta_2Al ", Acta Chem. Scand., 14, 1219 (1960).
- (268) Brukl, C., Nowotny, H., and Benesovsky, F., "Untersuchungen in den Dreistoff systemen: V-Al-Si, Nb-Al-Si, Cr-Al-Si, Mo-Al-Si bzw. Cr(Mo)-Al-Si", Mh. Chemie, 92 (5), 967-980 (1961).
- (269) Popov, I. A., and Rabezova, V. I., "Equilibrium Phase Diagram of the Niobium-Titanium-Aluminum System", Zhur. Neorg. Khim., 7, 436-39 (1962).
- (270) Nowotny, H., Benesovsky, F., Rudy, E., and Wittmann, A., "Aufbau und Zunderverhalten von Niob-Bor-Silicium-Legierungen", Monatsh. Chemie, 91 (5), 975-990 (1960).
- (271) Rudy, E., "Über Hafniumkarbid enthaltende Karbedsysteme", Mh. Chem., 91 (1), 180-181 (1960).
- (272) Benesovsky, F., and Rudy, E., "Zur Kenntnis der Systeme Uran-Zirkonium-(Hafnium, Niob, Tantal) Kohlenstoff", Plansee Pulvermetal., 9, 65-76 (1961).
- (273) Svechnikov, V. N., and Pan, V. M., "An Investigation of the Chromium-Nickel-Niobium Ternary System", Issledovaniya Po Zharoprochnym Splavam, 6, 240-250 (1960).
- (274) Goldschmidt, H. J., and Brand, J. A., "The Constitution of the Chromium-Niobium-Silicon System", J. Less-Common Metals, 3, 34-43 (1961).
- (275) Svechnikov, V. N., Kocherzhinskiy, Yu. A., Maystrenko, Ye. Ye., Pan, V. M., and Shurin, A. K., "A Study of the System Cr-Nb-V", Voprosy fiziki metallov i metallovedeniya, Kiev (1959), pp 120-132.
- (276) Vogel, R., and Bleichroth, W., "Das Dreistoffsystem Eisen-Phosphor-Niob", Arch. Eisenhutten., 33 (3), 208 (1962).
- (277) Rudy, E., Benesovsky, F., and Sedlatschek, K., "Untersuchungen im System Niob-Molybdän-Kohlenstoff", Mh. Chemie, 92 (4), 841-855 (1961).
- (278) Goldschmidt, H. J., and Brand, J. A., "The Constitution of the Chromium-Niobium-Molybdenum System", J. Less Common Metals, 3, 44-61 (1961).
- (279) Zakharova, M. I., Prokoshkin, D. A., "Examination of the Niobium-Molybdenum-Chromium System", Izvest. Akad. Nauk S.S.S.R., Otdel. Tekh. Nauk, Met. I. Topliva, 4, 59-67 (1961).

- (280) Ivanov, V. E., and Badajeva, T. A., "Phase Diagrams of Certain Ternary Systems of Uranium and Thorium", Proceedings of the Second United Nations International Conference on the Peaceful Uses of Atomic Energy", 6, 139-155 (1958).
- (281) Elliott, R. P., and Komjathy, S., "Niobium Phase Diagrams", Armour Research Foundation, USAEC Contract No. AT(11-1)-515, May 15, 1960.
- (282) Mikheev, V. S., and Belousov, O. K., "Fusion Diagram of the System Titanium-Zirconium-Niobium", Zhur. Neorg. Khim, 6, 1905-08 (1961).
- (283) Guard, R. W., and Smith, E. A., "Constitution of Nickel-Base Ternary Alloys, Ni-Mo-Al and Ni-Mo-Si Systems", J. Inst. Metals, 88, 283-287 (February, 1960).
- (284) Kolomytsev, P. T., et al., "Phase-Compositions of the System Nickel-Molybdenum-Boron", Atomnaya Energiya, 10, 276-277 (March, 1961).
- (285) Wittmann, A., Nowotny, H., and Boller, H., "Ein Beitrag zum Dreistoff Titan-Molybdän-Bor", Mh. Chem., 91 (4), 608-619 (1960).
- (286) Vogel, R., and Gerhardt, R., "Das System Eisen-Molybdän-Silizium", Arch. Eisenhutten., 32 (1), 53 (1961).
- (287) Kornilov, I. I., Polyakova, R. S., "Examination into Properties of Alloys of Titanium-Vanadium-Molybdenum System", Izvest. Akad. Nauk S.S.S.R., Otdel Tekh. Nauk, Met. I. Toplivo, 4, 76-82 (1961).
- (288) Grum-Grzhimailu, N. V., and Prokof'ev, D. I., "X-ray Investigation at High Temperatures of Solid Solutions of the System Chromium-Tungsten-Molybdenum", Zhur. Neorg. Khim., 6, 1154-64 (1961).
- (289) Lavendel, H. W., "Alloys of Tantalum Diboride With Iron, Cobalt, and Nickel", Plansee Pulvermet., 9 (1-2), 80-95 (1961).
- (290) Köster, W., and Becker, C., "The System Iron-Cobalt-Tantalum", Arch. Eisenhüttenwesen, 8, 557-560 (1935).
- (291) Pitman, D. T., and Das, D. K., "A Study of the Thorium-Tungsten-Boron System", J. Electrochem Soc., 107 (9), 763-66 (1960).
- (292) Rudy, Erwin, Rudy, Elisabeth, and Benesovsky, F., "Untersuchungen in den Systemen Thorium-Wolfram-Kohlenstoff und Uran-Wolfram-Kohlenstoff, Monatsh. Chemie, 93 (2), 532-534 (1962).
- (293) Köster, W., "The Ternary System Cobalt-Chromium-Tungsten", Z. Metallkunde, 25, 22-27 (1933).
- (294) Kieffer, R., Schob, O., Nowotny, H., and Benesovsky, F., "Untersuchungen in den Dreistoffen: Cr-W-Si and Mo-W-Si", Monatsh. Chemie, 93 (2), 519-521 (1962).

- (295) Köster, W., and Tonn, W., "The System Iron-Cobalt-Tungsten", Arch. Eisenhüttenwesen, 5, 431-440 (1932).
- (296) Vogel, R., and Weizenkorn, H., "Über das Dreistoffsystem Eisen-Schwefel-Wolfram", Arch. Eisenhüttenwesen, 32 (6), 419 (1961).
- (297) Nowotny, H., Benesovsky, F., and Brukl, C., "Untersuchungen im System: Wolfram-Silicium-Germanium", Mh. Chemie, 92 (2), 365-370 (1961).
- (298) Savitskii, E. M., and Kopetskii, Ch. V., "Phase Diagram of the Manganese-Tantalum System", Zhur. Neorg. Khimii, 5 (11), 2638 (1960).
- (299) Savitskii, E. M., and Kopetskii, Ch. V., "Physicochemical Behavior of Manganese with Niobium", Zhur. Neorg. Khimii, 5 (3), 755 (1960).
- (300) Gregor'ev, A. T., Sokolovskaya, E. M., Maksimova, M. V., Sokolova, I. G., and Nedumov, N. A., "Polymorphic Transformations of Chromium in Alloys With Tantalum", Zhur. Neorg. Khimii, 5 (11), 2640 (1960).
- (301) Wyder, W. C., and Hoch, M., "The System Niobium (Columbium)-Titanium-Zirconium-Oxygen at 1500 C", Naval Research Contract Nonr-2168(02), Project NR 039-032; also AIME Trans, 224, 373-378 (1962).
- (302) Budberg, P. B., "Study of Alloys of the Ternary System Nickel-Aluminum-Tungsten", Zhur. Neorg. Khimii, 3 (3), 694-698 (1958).
- (303) Savitsky, Ye. M., and Baron, V. V., "Investigation of the System Vanadium-Molybdenum-Silicon", Zhur. Neorg. Khimii, 7 (5), 1117-1125 (1962).
- (304) Wyman, L. L., Cuthill, J. R., Moore, G. A., Park, J. J., and Yakowitz, H., "Intermediate Phases in Superconducting Niobium-Tin Alloys", Journal Research Nat. Bur. Standards - A. Physics and Chemistry, 66A (4), 351-63 (July-August, 1962).
- (305) Dragsdorf, R. D., and Forgeng, W. D., "The Intermetallic Phases in the Cobalt-Tantalum System", Acta Cryst., 15 (6), 531-534 (1962).
- (306) McMasters, O. D., and Larsen, W. L., "Phase Equilibria in the Thorium-Tantalum System", J. Less-Common Metals, 3, 312-320 (1961).
- (307) Anderson, E., and Hume-Rothery, W., "The Equilibrium Diagram of the System Molybdenum-Rhodium", J. Less-Common Metals, 2, 19-28 (1960).
- (308) Petzow, G., and Gitlesen, G., "Aufbau und Eigenschaften von Uran-Vanadium-Molybdän Legierungen", Z. Metallkde., 53 (8), 519-520 (1962).
- (309) Rudy, Erwin, Benesovsky, F., and Rudy, Elizabeth, "The System Vanadium-Tungsten-Carbon", Monatsh. Chemie, 93, 693-707 (1962).
- (310) Glazov, V. M., and Mal'tsev, M. V., "Study of the Al-Ta Phase Diagram", Izvest. Akad. Nauk, S.S.S.R., Otdel. Tekh. Nauk., No. 4, 131-36 (1956).

- (311) Baron, V. V., Yefimov, Yu. V., and Savitskiy, Ye. M., "Structure and Properties of the Alloys of the Vanadium-Molybdenum System", *Izvest. Akad. Nauk, S.S.S.R., Otdel. Tekh. Nauk*, No. 4, 36-40 (1958).
- (312) Guard, R. W., and Smith, E. A., "Constitution of Nickel-Base Ternary Alloys. IV. Nickel-Molybdenum-Titanium System", *J. Inst. Metals*, 88, 369-374 (1960).
- (313) Vogel, R., and Horstmann, D., "The Iron-Iron Phosphide-Molybdenum Phosphide-Molybdenum Constitution Diagram", *Arch. Eisenhüttenwesen*, 24, 369-374 (1954).
- (314) Hoch, M., and Desjardins, M., "The System Molybdenum-Titanium-Zirconium-Oxygen at 1500 C", *Trans. AIME*, 224, 821-827 (August, 1962).
- (315) Nowotny, H., Lux, B., and Kudielka, H., "The Behavior of High-Melting Metal Silicides With Respect to Boron, Carbon, Nitrogen and Oxygen", *Monatsh. Chemie*, 87 (3), 447-470 (1956).
- (316) Kudielka, H., and Nowotny, H., "Disilicide Systems", *Monatsh. Chemie*, 87 (3), 471-482 (1956).
- (317) Mints, R. S., Byelyayeva, G. F., and Malkov, Yoo. S., "Constitution Diagram of the System $\text{Ni}_3\text{Al-Ni}_3\text{Nb}$ ", *Zhur. Neorg. Khim.*, 7 (10), 2382-2387 (1962).
- (318) Bannister, G. H., and Murray, J. R., "Some Observations on Uranium-Molybdenum-Niobium Alloys", *J. Less-Common Metals*, 2, 372-382 (1960).
- (319) Savitskiy, E. M., and Zakharov, A. M., "Phase Diagrams of the Ternary System Niobium-Tungsten-Zirconium", *J. Neorg. Khimii*, 7 (11), 2575-2580 (1962).
- (320) Kubaschewski, O., and Speidel, H., "Oxidation Resistance and Some Phase Relationships in the System Chromium-Tantalum-Nickel", *J. Inst. Metals*, 75, 417-430 (1948-49).
- (321) Dokukina, N. V., and Shamrai, F. I., "Phase Equilibrium in the System W-Nb-Si and Some Properties of Alloys", *Poroshkovaya Met., Akad. Nauk Ukr. SSR*, 2 (6), 32-41 (1962).
- (322) Clare, J. W. H., "Compounds Present in Aluminum-Rich Alloys of the Aluminum-Molybdenum System", *J. Inst. Metals*, 89, 232-234 (1960-61).
- (323) Auld, J. H., and Ryan, N. E., "The Solid Solubility of Tantalum in Chromium", *J. Less-Common Metals*, 3, 221-225 (1961).
- (324) Hartley, C. S., Baum, W. L., Fisher, D. W., and Rapperport, E. S., "Phase Relationships in Tantalum-Rich Tantalum-Ruthenium Alloys at 1500 C", *WADD-TN-60-288*, March, 1961.
- (325) Deardorf, D. K., and Kato, H., "The Constitution Diagram of Tungsten-Hafnium. Discussion", *Trans. AIME*, 227, 264-65 (1963).

LIST OF DMIC TECHNICAL REPORTS ISSUED
DEFENSE METALS INFORMATION CENTER

Battelle Memorial Institute

Columbus 1, Ohio

Copies of the technical reports listed below may be obtained from DMIC at no cost by Government agencies, and by Government contractors, subcontractors, and their suppliers. Others may obtain copies from the Office of Technical Services, Department of Commerce, Washington 25, D. C. See PB numbers and prices in parentheses.

DMIC Report Number	Title
46D	Department of Defense Titanium Sheet-Rolling Program - Uniform Testing Procedure for Sheet Materials, September 12, 1958 (PB 121649 \$1.25)
46E	Department of Defense Titanium Sheet-Rolling Program - Thermal Stability of the Titanium Sheet-Rolling-Program Alloys, November 25, 1958 (PB 151061 \$1.25)
46F	Department of Defense Titanium Sheet-Rolling Program Status Report No. 4, March 20, 1959 (PB 151065 \$2.25)
46G	Department of Defense Titanium Sheet-Rolling Program - Time-Temperature-Transformation Diagrams of the Titanium Sheet-Rolling Program Alloys, October 19, 1959 (PB 151075 \$2.25)
46H	Department of Defense Titanium Sheet-Rolling Program, Status Report No. 5, June 1, 1960 (PB 151087 \$2.00)
46I	Statistical Analysis of Tensile Properties of Heat-Treated Ti-4A1-3Mo-1V Sheet, September 16, 1960 (PB 151095 \$1.25)
46J	Statistical Analysis of Tensile Properties of Heat-Treated Ti-4A1-3Mo-1V and Ti-2.5A1-16V Sheet (AD 259284 \$1.25)
106	Beryllium for Structural Applications, August 15, 1958 (PB 121648 \$3.00)
107	Tensile Properties of Titanium Alloys at Low Temperature, January 15, 1959 (PB 151062 \$1.25)
108	Welding and Brazing of Molybdenum, March 1, 1959 (PB 151063 \$1.25)
109	Coatings for Protecting Molybdenum From Oxidation at Elevated Temperature, March 6, 1959 (PB 151064 \$1.25)
110	The All-Beta Titanium Alloy (Ti-13V-11Cr-3Al), April 17, 1959 (PB 151066 \$3.00)
111	The Physical Metallurgy of Precipitation-Hardenable Stainless Steels, April 20, 1959 (PB 151067 \$2.00)
112	Physical and Mechanical Properties of Nine Commercial Precipitation-Hardenable Stainless Steels, May 1, 1959 (PB 151068 \$3.25)
113	Properties of Certain Cold-Rolled Austenitic Stainless Sheet Steels, May 15, 1959 (PB 151069 \$1.75)
114	Ductile-Brittle Transition in the Refractory Metals, June 25, 1959 (PB 151070 \$2.00)
115	The Fabrication of Tungsten, August 14, 1959 (PB 151071 \$1.75)
116R	Design Information on 5Cr-Mo-V Alloy Steels (H-11 and 5Cr-Mo-V Aircraft Steel) for Aircraft and Missiles (Revised), September 30, 1960 (PB 151072-R \$1.50)
117	Titanium Alloys for High-Temperature Use Strengthened by Fibers or Dispersed Particles, August 31, 1959 (PB 151073 \$2.00)
118	Welding of High-Strength Steels for Aircraft and Missile Applications, October 12, 1959 (PB 151074 \$2.25)
119	Heat Treatment of High-Strength Steels for Aircraft Applications, November 27, 1959 (PB 151076 \$2.50)
120	A Review of Certain Ferrous Castings Applications in Aircraft and Missiles, December 18, 1959 (PB 151077 \$1.50)
121	Methods for Conducting Short-Time Tensile, Creep, and Creep-Rupture Tests Under Conditions of Rapid Heating, December 20, 1959 (PB 151078 \$1.25)
122	The Welding of Titanium and Titanium Alloys, December 31, 1959 (PB 151079 \$1.75)
123	Oxidation Behavior and Protective Coatings for Columbium and Columbium-Base Alloys, January 15, 1960 (PB 151080 \$2.25)
124	Current Tests for Evaluating Fracture Toughness of Sheet Metals at High Strength Levels, January 28, 1960 (PB 151081 \$2.00)
125	Physical and Mechanical Properties of Columbium and Columbium-Base Alloys, February 22, 1960 (PB 151082 \$1.75)
126	Structural Damage in Thermally Cycled René 41 and Astroloy Sheet Materials, February 29, 1960 (PB 151083 \$0.75)
127	Physical and Mechanical Properties of Tungsten and Tungsten-Base Alloys, March 15, 1960 (PB 151084 \$1.75)
128	A Summary of Comparative Properties of Air-Melted and Vacuum-Melted Steels and Superalloys, March 28, 1960 (PB 151085 \$2.75)
129	Physical Properties of Some Nickel-Base Alloys, May 20, 1960 (PB 151086 \$2.75)
130	Selected Short-Time Tensile and Creep Data Obtained Under Conditions of Rapid Heating, June 17, 1960 (PB 151088 \$2.25)
131	New Developments of the Welding of Metals, June 24, 1960 (PB 151089 \$1.25)
132	Design Information on Nickel-Base Alloys for Aircraft and Missiles, July 20, 1960 (PB 151090 \$3.00)
133	Tantalum and Tantalum Alloys, July 25, 1960 (PB 151091 \$5.00)
134	Strain Aging of Refractory Metals, August 12, 1960 (PB 151092 \$1.75)
135	Design Information on PH 15-7 Mo Stainless Steel for Aircraft and Missiles, August 22, 1960 (PB 151093 \$1.25)

DMIC Report Number	Title
136A	The Effects of Alloying Elements in Titanium, Volume A. Constitution, September 15, 1960 (PB 151094 \$3.50)
136B	The Effects of Alloying Elements in Titanium, Volume B. Physical and Chemical Properties, Deformation and Transformation Characteristics, May 29, 1961 (AD 260226 \$3.00)
137	Design Information on 17-7 PH Stainless Steels for Aircraft and Missiles, September 23, 1960 (PB 151096 \$1.00)
138	Availability and Mechanical Properties of High-Strength Steel Extrusions, October 26, 1960 (PB 151097 \$1.75)
139	Melting and Casting of the Refractory Metals Molybdenum, Columbium, Tantalum, and Tungsten, November 18, 1960 (PB 151098 \$1.00)
140	Physical and Mechanical Properties of Commercial Molybdenum-Base Alloys, November 30, 1960 (PB 151099 \$3.00)
141	Titanium-Alloy Forgings, December 19, 1960 (PB 151100 \$2.25)
142	Environmental Factors Influencing Metals Applications in Space Vehicles, December 27, 1960 (PB 151101 \$1.25)
143	High-Strength-Steel Forgings, January 5, 1961 (PB 151102 \$1.75)
144	Stress-Corrosion Cracking - A Nontechnical Introduction to the Problem, January 6, 1961 (PB 151103 \$0.75)
145	Design Information on Titanium Alloys for Aircraft and Missiles, January 10, 1961 (PB 151104 \$2.25)
146	Manual for Beryllium Prospectors, January 18, 1961 (PB 151105 \$1.00)
147	The Factors Influencing the Fracture Characteristics of High-Strength Steel, February 6, 1961 (PB 151106 \$1.25)
148	Review of Current Data on the Tensile Properties of Metals at Very Low Temperatures, February 14, 1961 (PB 151107 \$2.00)
149	Brazing for High Temperature Service, February 21, 1961 (PB 151108 \$1.00)
150	A Review of Bending Methods for Stainless Steel Tubing, March 2, 1961 (PB 151109 \$1.50)
151	Environmental and Metallurgical Factors of Stress-Corrosion Cracking in High-Strength Steels, April 14, 1961 (PB 151110 \$0.75)
152	Binary and Ternary Phase Diagrams of Columbium, Molybdenum, Tantalum, and Tungsten, April 28, 1961 (AD 257739 \$3.50)
153	Physical Metallurgy of Nickel-Base Superalloys, May 5, 1961 (AD 258041 \$1.25)
154	Evolution of Ultrahigh-Strength, Hardenable Steels for Solid-Propellant Rocket-Motor Cases, May 25, 1961 (AD 257976 \$1.25)
155	Oxidation of Tungsten, July 17, 1961 (AD 263598 \$3.00)
156	Design Information on AM-350 Stainless Steel for Aircraft and Missiles, July 28, 1961 (AD 262407 \$1.50)
157	A Summary of the Theory of Fracture in Metals, August 7, 1961 (PB 181081 \$1.75)
158	Stress-Corrosion Cracking of High-Strength Stainless Steels in Atmospheric Environments, September 15, 1961 (AD 266005 \$1.25)
159	Gas-Pressure Bonding, September 25, 1961 (AD 265133 \$1.25)
160	Introduction to Metals for Elevated-Temperature Use, October 27, 1961 (AD 268647 \$2.50)
161	Status Report No. 1 on Department of Defense Refractory Metals Sheet-Rolling Program, November 2, 1961 (AD 267077 \$1.00)
162	Coatings for the Protection of Refractory Metals From Oxidation, November 24, 1961 (AD 271384 \$3.50)
163	Control of Dimensions in High-Strength Heat-Treated Steel Parts, November 29, 1961 (AD 270045 \$1.00)
164	Semiaustenitic Precipitation-Hardenable Stainless Steels, December 6, 1961 (AD 274805 \$2.75)
165	Methods of Evaluating Welded Joints, December 28, 1961 (AD 272088 \$2.25)
166	The Effect of Nuclear Radiation on Structural Metals, September 15, 1961 (AD 265839 \$2.50)
167	Summary of the Fifth Meeting of the Refractory Composites Working Group, March 12, 1962 (AD 274804 \$2.00)
168	Beryllium for Structural Applications, 1958-1960, May 18, 1962 (AD 278723 \$3.50)
169	The Effect of Molten Alkali Metals on Containment Metals and Alloys at High Temperatures, May 18, 1962 (AD 282932 \$1.50)
170	Chemical Vapor Deposition, June 4, 1962 (AD 281887 \$2.25)
171	The Physical Metallurgy of Cobalt-Base Superalloys, July 6, 1962 (AD 283356 \$2.25)
172	Background for the Development of Materials To Be Used in High-Strength-Steel Structural Weldments, July 31, 1962 (AD 284265 \$3.00)
173	New Developments in Welded Fabrication of Large Solid-Fuel Rocket-Motor Cases, August 6, 1962 (AD 284829 \$1.00)
174	Electron-Beam Processes, September 15, 1962 (AD 287433 \$1.75)
175	Summary of the Sixth Meeting of the Refractory Composites Working Group, September 24, 1962 (AD 287029 \$1.75)
176	Status Report No. 2 on Department of Defense Refractory Metals Sheet-Rolling Program, October 15, 1962 (AD 288127 \$1.25)
177	Thermal Radiative Properties of Selected Materials, November 15, 1962, Vol. I (AD 294345 \$3.00)
177	Thermal Radiative Properties of Selected Materials, November 15, 1962, Vol. II (AD 294346 \$4.00)
178	Steels for Large Solid-Propellant Rocket-Motor Cases, November 20, 1962
179	A Guide to the Literature on High-Velocity Metalworking, December 3, 1962
180	Design Considerations in Selecting Materials for Large Solid-Propellant Rocket-Motor Cases, December 10, 1962
181	Joining of Nickel-Base Alloys, December 20, 1962
182	Structural Considerations in Developing Refractory Metal Alloys, January 31, 1963

Battelle Memorial Institute, Defense Metals Information Center, Columbus, Ohio, BINARY AND TERNARY PHASE DIAGRAMS OF COLUMBIUM, MOLYBDENUM, TANTALUM, AND TUNGSTEN (Supplement to DMIC Report 152), by J. J. English. 7 February 1963, 131 pp incl. illus. 92 refs. DMIC Report 183. [AF 33(616)-7747] Unclassified report This report contains a compilation of binary and ternary phase diagrams of the four refractory metals columbium, molybdenum, tantalum, and tungsten. Included with each binary diagram and with some ternary diagrams is a short discussion which lists information such as maximum solubility and crystal structures of intermediate phases.	UNCLASSIFIED 1. Columbium - Phase studies 2. Niobium - Phase studies 3. Molybdenum - Phase studies 4. Tantalum - Phase studies 5. Tungsten - Phase studies I. English, J. J. II. Defense Metals Information Center III. Contract AF 33(616)-7747 UNCLASSIFIED	Battelle Memorial Institute, Defense Metals Information Center, Columbus, Ohio, BINARY AND TERNARY PHASE DIAGRAMS OF COLUMBIUM, MOLYBDENUM, TANTALUM, AND TUNGSTEN (Supplement to DMIC Report 152), by J. J. English. 7 February 1963, 131 pp incl. illus. 92 refs. DMIC Report 183. [AF 33(616)-7747] Unclassified report This report contains a compilation of binary and ternary phase diagrams of the four refractory metals columbium, molybdenum, tantalum, and tungsten. Included with each binary diagram and with some ternary diagrams is a short discussion which lists information such as maximum solubility and crystal structures of intermediate phases.	UNCLASSIFIED 1. Columbium - Phase studies 2. Niobium - Phase studies 3. Molybdenum - Phase studies 4. Tantalum - Phase studies 5. Tungsten - Phase studies I. English, J. J. II. Defense Metals Information Center III. Contract AF 33(616)-7747 UNCLASSIFIED	Battelle Memorial Institute, Defense Metals Information Center, Columbus, Ohio, BINARY AND TERNARY PHASE DIAGRAMS OF COLUMBIUM, MOLYBDENUM, TANTALUM, AND TUNGSTEN (Supplement to DMIC Report 152), by J. J. English. 7 February 1963, 131 pp incl. illus. 92 refs. DMIC Report 183. [AF 33(616)-7747] Unclassified report This report contains a compilation of binary and ternary phase diagrams of the four refractory metals columbium, molybdenum, tantalum, and tungsten. Included with each binary diagram and with some ternary diagrams is a short discussion which lists information such as maximum solubility and crystal structures of intermediate phases.	UNCLASSIFIED 1. Columbium - Phase studies 2. Niobium - Phase studies 3. Molybdenum - Phase studies 4. Tantalum - Phase studies 5. Tungsten - Phase studies I. English, J. J. II. Defense Metals Information Center III. Contract AF 33(616)-7747 UNCLASSIFIED
--	---	--	---	--	---