

UNCLASSIFIED

AD . 4 2 2 4 8 6

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

AD 422486

ONR Contract No. Nonr 591-(10)

Technical Report No. 18

R.P.I. Project No. 441.35


November, 1963

CORROSION STUDIES IN MOLTEN ALKALI CARBONATES
PART III, GOLD-PALLADIUM, NICKEL, AND STAINLESS STEEL-347

by

G.J. Janz and A. Conte

Department of Chemistry
Rensselaer Polytechnic Institute
Troy, N.Y.

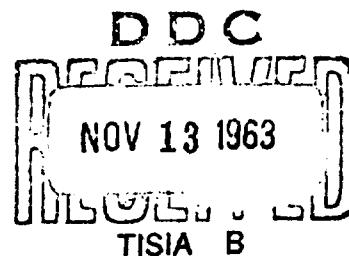

Submitted: Corrosion (National Association Corrosion Engineers)
November, 1963

CORROSION OF GOLD-PALLADIUM, NICKEL, AND STAINLESS STEEL (347)
IN MOLTEN ALKALI CARBONATES

by

George J. Janz and A. Conte[†]

Rensselaer Polytechnic Institute, Department of Chemistry, Troy, N.Y.

Results are reported on the ability of gold-palladium, nickel, and columbium-stabilized stainless steel to withstand chemical attack in molten alkali carbonates for prolonged periods at high temperatures (600° - 700°C). The nature of the products formed, and the extent of corrosion were investigated as an extension of the studies on the noble metals, silver, and refractories described in the preceding communication.¹

EXPERIMENTAL AND RESULTS

The preparation of the ternary eutectic mixture of Li_2CO_3 , Na_2CO_3 and K_2CO_3 and the apparatus for the weight-loss corrosion tests have been given in detail elsewhere¹; it is sufficient to note that CO_2 gas atmosphere (1 atm press) was maintained above the melt for all the measurements. The metals, highest purity specimens commercially available, were used without further treatment.

To gain information on the nature of the products formed, a series of measurements were undertaken for prolonged periods at 700°C as described previously¹. After the experiments, the specimens were boiled in water to remove carbonates and soluble corrosion products. The nature of the film on

[†] Post-Doctoral Research Fellow: Present Address: Laboratorio di Chimica delle Radiazioni e Chimica Nucleare, Istituto di Chimica Generale, Citta Universitaria, Roma, Italia.

the surface of the specimens was examined by X-ray diffraction methods (Cu K_{α} ; 35 kV; 10 ma; 6-12 hrs). The results for the nickel and 347 stainless steel tests are in Table 1 together with the literature values² for NiO and LiFeO_2 . On the Au-20% Pd alloy surface, after such tests, a faintly colored film was visible to the eye; X-ray results only confirmed the presence of the unchanged alloy surface. The thickness of the film was apparently insufficient for the conventional X-ray diffraction methods and this work was not pursued further.

A series of weight-loss measurements for each specimen in the presence of added oxides in the carbonate melts (by virtue of the sintered Al_2O_3 crucible technique¹) and in the pure carbonate melts were also undertaken to gain some quantitative measure of the ability of these metals to withstand corrosion. The results are in Table 2.


DISCUSSION

The X-ray diffraction data (Table 1) leave little doubt that the products for the chemical attack by molten carbonates at 700°C on nickel and 347 stainless steel are, respectively, NiO and LiFeO_2 . The nature of the product of the small but finite attack of the Au-Pd (20%) alloy can be inferred from the known formation³ of sodium palladate when palladium is exposed to molten Na_2CO_3 ; the film detected by visual inspection is likely an oxide (possibly a palladate), but exact confirmation must await additional analytical studies.

The nickel attack was further investigated by using a pure nickel crucible to contain the molten carbonates at 600°C and at 710°C for 24 hour periods, respectively. At the lower temperature the crucible walls were

uniformly covered with the oxide coatings; at the higher temperature the oxide coating was severe and the crucible walls were embrittled. It is known⁴ that intercrystalline precipitation of graphite and NiO occurs when nickel is exposed at elevated temperatures to carburizing atmospheres. This factor and the possible formation for NiO through the decomposition at 600-700°C of the thermodynamically unstable NiCO₃ being formed as a "soluble" corrosion product, are undoubtedly contributing factors to the nickel corrosion processes under the environmental conditions of these experiments.

The weight-loss experiments (Table 2) show that the changes in the presence of added oxide ions (i.e. Al₂O₃) are as would be predicted in the Mass Law shifts for ^{the overall} equilibria of the type:

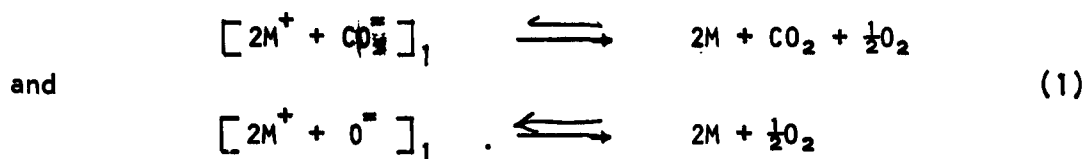

The oxidant initiating the metal attack is undoubtedly present as an impurity in trace amounts; rigorous exclusion of air (oxygen) in such melts is difficult.

Comparison of the results for the niobium-stainless steel (347) with Au-Pd (20%) in Table 2, and the noble metals in the preceding communication¹ reveals that this metal is quite highly resistant to attack; the oxide film (LiFeO₂) suggests the possibility of passivity. It is known that passivity can be conferred by use of a galvanic couple of the active-passive specimen and a more noble metal⁵. The result of such an exploratory experiment is given in Table 2. A small but significant measure of protection can be inferred if the decreased weight change is truly significant. Electrochemical studies using a potentiostatic polarization technique are being initiated in This Laboratory to gain additional information on these processes.

ACKNOWLEDGMENTS

We thank Dr. Norbert D. Greene for helpful discussions, particularly relative to the exploratory galvanic couple experiment. This work was made possible, in large part, by financial support from the U.S. Department of the Navy, Office of Naval Research, Chemistry Division, Washington, D.C.

REFERENCES

1. G.J. Janz, A. Conte, and E. Neuenschwander; *J. Corrosion*, 19, 292t (1963)
2. A.S.T.M. X-Ray Diffraction Data Reference Index (1962)
3. J.G. Scheer, E.A. Van Arkel, and R.D. Heyding; *Can. J. Res.* 33, 683 (1955)
4. H. Uhlig; *Corrosion Handbook*, J. Wiley and Sons (N.Y.), (1958)
5. M. Stern; *J. Electrochem. Soc.* 105, 638 (1958)

TABLE 1

DEBYE-SCHERRER X-RAY RESULTS FOR CORROSION PRODUCTS

<u>Nickel in Molten Carbonates</u>			
d(Å) obs'd intensity	2.09 v.s.	2.41 s.	1.48 m.
d(Å) literature (N10)	2.09	2.41	1.48

<u>Type 347 Stainless Steel in Molten Carbonates</u>			
d(Å) obs'd intensity	2.06 s.	1.47 m.	2.39 w.
d(Å) literature [†] (LiFeO ₂)	2.07	1.47	2.39

[†] literature values taken for A.S.T.M. X-Ray Diffraction Reference Index (1962)

Table 2

STATIC CORROSION EXPERIMENTS: Au-20% Pd ALLOY, NICKEL
AND TYPE 347 STAINLESS STEEL IN THE MOLTEN Li, Na, AND K
CARBONATE EUTECTIC MIXTURE UNDER CO₂ ATMOSPHERES

Temperature (°C)	Crucible Type	Time (Hrs)	Sample	
			Area (cm ²)	Change mg hr cm ⁻²
<u>Au-20% Pd Alloy</u>				
740°	sintered Al ₂ O ₃	96	1.90	+0.001
740°	Au-20% Pd	96	2.63	+0.010
<u>Nickel</u>				
670°	sintered Al ₂ O ₃	63	2.16	-0.010
670°	Au	63	2.60	-0.017
<u>Type 347 Stainless Steel</u>				
730°	sintered Al ₂ O ₃	94	-5.0	-0.003
730°	Au-20% Pd	95	5.5	+0.023
730°	Au-20% Pd	93	8.2 [‡]	+0.016

‡ The stainless-steel sample was galvanically coupled with platinum, both totally immersed in the melt.

TECHNICAL REPORT DISTRIBUTION LIST

Commanding Officer Office of Naval Research Branch Office 230 N. Michigan Avenue Chicago 1, Illinois (1)	U.S. Army Natick Laboratories Clothing and Organic Materials Division Natick, Massachusetts Attn: Associate Directory (1)
Commanding Officer Office of Naval Research Branch Office 207 West 24th Street New York 11, New York (1)	Harry Diamond Laboratories Washington 25, D.C. Attn: Library (1)
Commanding Officer Office of Naval Research Branch Office 1030 East Green Street Pasadena 1, California (1)	Office, Chief of Research and Development Department of the Army Washington 25, D.C. Attn: Physical Sciences Division (1)
Commanding Officer Office of Naval Research Branch Office Box 39, Navy 100, F.P.O. New York, N.Y. (7)	Chief, Bureau of Ships Department of the Navy Washington 25, D.C. Attn: Code 342A (2)
Director, Naval Research Laboratory Washington 25, D.C. Attn: Technical Information Officer (6) Chemistry Division (2) Code 6160 (1)	Technical Library Library, DLI-3 Bureau of Naval Weapons Department of the Navy Washington 25, D.C. (4)
Chief of Naval Research Department of the Navy Washington 25, D.C. Attn: Code 425 (2)	Defense Documentation Center Cameron Station Alexandria, Virginia (20)
DDR and E Technical Library Room 3C-128, The Pentagon Washington 25, D.C. (1)	Commanding Officer U.S. Army Electronics Research and Development Laboratory Attn: SELRA/DR Fort Monmouth, New Jersey 07703 (1)
Department of the Army Supply and Maintenance Command Maintenance Readiness Division Washington 25, D.C. Attn: Technical Director (1)	Naval Radiological Defense Laboratory San Francisco 24, California Attn: Head, Chemistry Division (1)

REVISÉD 30 AUG 1963

•

Technical Report Distribution List

Page 2

Commanding Officer
Army Research Office
Box CM, Duke Station
Durham, North Carolina
Attn: CRD-AA-IP (1)

Atomic Energy Commission
Division of Research
Chemistry Programs
Washington 25, D.C. (1)

Atomic Energy Commission
Division of Technical Information Ext.
Post Office Box 62
Oak Ridge, Tennessee (1)

Commanding Officer
U.S. Army Chemical Research and
Development Laboratories
Attn: Librarian (1)
Edgewood Arsenal, Maryland

Dr. Norman Hackerman
Department of Chemistry
University of Texas
Austin, Texas (1)

Dr. Paul Delahay
Department of Chemistry
Louisiana State University
Baton Rouge, Louisiana (1)

Dr. J. O'M Bockris
Department of Chemistry
University of Pennsylvania
Philadelphia, Pennsylvania (1)

Dr. R.R. Heikes
Solid State Phenomena Department
Westinghouse Electric Corporation
Pittsburgh, Pennsylvania (1)

Dr. Ernest Yeager
Department of Chemistry
Western Reserve University
Cleveland 6, Ohio (1)

Dr. Pierre van Rysselberghe
Department of Chemistry
Stanford University
Palo Alto, California (1)

Dr. A. Patterson, Jr.
Department of Chemistry
Yale University
New Haven, Connecticut (1)

Mr. M.F. Blackburn
E.R.D.L.
Materials Branch
Fort Belvoir, Virginia (1)

Mr. W.M. Lee, Director
Contract Research Department
Pennsalt Chemicals Corporation
900 First Avenue
King of Prussia, Pa. (2)

Dr. B.R. Sundheim
Department of Chemistry
New York University
New York 3, New York (1)

Commanding Officer
U.S. Naval Ordnance Laboratory
Corona, California
Attn: Library (1)

Dr. Morris Eisenberg
Electrochimica Corporation
307 Diablo Court
Palo Alto, California (1)

Technical Report Distribution List

Page 3

U.S. Naval Applied Science Laboratory Technical Library Building 291, Code 9832 Naval Base Brooklyn, N.Y. 11251	(1)	Dr. A.C. Makrides Tyco, Inc. Bear Hill Waltham, Massachusetts	(1)
E.C. Wadlow Department of Material Research Queen Anne Mansions St. James Park London, S.W. 1 VIA: Commanding Officer Office of Naval Research Branch Office Navy 100 Box 39, F.P.O. New York, N.Y.	(1)	Dr. G.C. Szego Institute for Defense Analysis 1666 Connecticut Avenue, N.W. Washington 9, D.C.	(1)
Monsanto Research Corporation Everett Station Boston 49, Massachusetts Attn: Library	(1)	Dr. S.P. Wolsky, Director Laboratory for Physical Science P.R. Mallory, Inc. N.W. Industrial Park Burlington, Mass.	(1)
Dr. E.M. Cohn NASA Code RPP 1512 H. Street, N.W. Washington 25, D.C.	(1)	Dr. A.B. Scott Department of Chemistry Oregon State University Corvallis, Or.	
Dr. M.S. Cohen, Chief Propellants Synthesis Section Reaction Motors Division Denville, New Jersey	(1)	Dr. Isaac Trachtenberg Energy Research Laboratory Texas Instruments Inc. Research Building 13500 North Central Expressway Dallas, Texas	(1)
Dr. Paul W. Gilles Department of Chemistry The University of Kansas Lawrence, Kansas	(1)	Aerospace Corporation P.O. Box 95085 Los Angeles 45, California Attn: Library Technical Documents Group	(1)
Dr. William T. Biedler Research Laboratories United Air Corp. Silver Lane East Hartford, 8, Conn.	(1)		