

UNCLASSIFIED

AD 429916

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED


NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

64-9

429916

CATALOGED BY DDC

AS AD No. _____

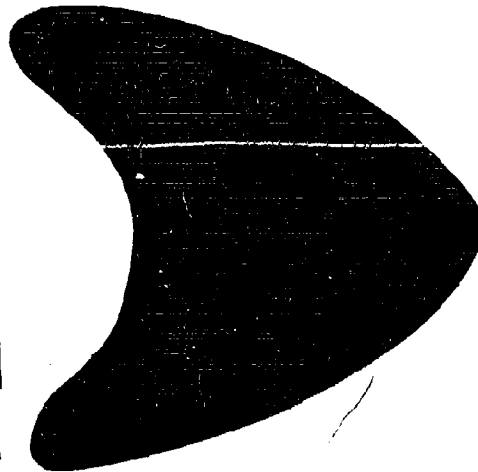

RESS

REPORT


SECOND QUARTER
OCTOBER - DECEMBER 1963

429916

DEVELOPMENT OF THIN ORGANIC
ROLLED FILM CAPACITOR



UNION CARBIDE CORPORATION
LINDE DIVISION
KEMET DEPARTMENT

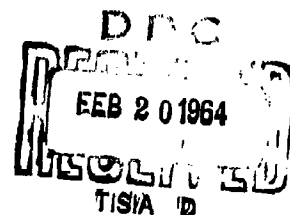

RESEARCH AND DEVELOPMENT WORK ON DEVELOPMENT
OF THIN ORGANIC ROLLED FILM CAPACITOR

BUREAU OF SHIPS CONTRACT NObsr-89519
SECOND QUARTERLY PROGRESS REPORT
OCTOBER 1, 1963 - DECEMBER 31, 1963

DEVELOPMENT OF THIN ORGANIC

ROLLED FILM CAPACITOR

BUREAU OF SHIPS CODE 606/681A2

SUBJECT

Bureau of Ships Contract NObsr-89519
Quarterly Research and Development Report,
October 1, 1963 - December 31, 1963

REFERENCE

Project Serial No. SR0080302 ST 9636

PROGRAM OBJECTIVES

To develop a capacitor, using ML-1 film as the dielectric, capable of 100 volt operation over the temperature range of -55 to 170°C, which is twenty times smaller than equivalent CQ05 per MIL Specification MIL-C-19978B. Such capacitor to exhibit dissipation of .01%; insulation resistance of at least 15 ohm farads at 170°C; temperature coefficient of less than 250 ppm/°C; 250% dielectric withstanding voltage; no capacitance shift with frequency; less than 5% change in capacitance after life test.

Approved by:



D. J. Valley, Project Leader



J. S. Wagener, Manager
Research and Development

Union Carbide Corporation
Linde Division, Kemet Department
Parma, Ohio

PERSONNEL

L. F. Athearn - Development Engineer
T. M. Adams - Assistant Development Engineer
C. W. Umbaugh - Assistant Development Engineer
R. L. Burdick - Technical Assistant
V. M. Kennedy - Technical Assistant
R. L. Prunty - Technical Assistant

TABLE OF CONTENTS

	<u>Page</u>
I. Substrate Preparation	1
A. Surface Decontamination	1
B. Mechanical Smoothing	1
C. Electrochemical Polishing	2
II. Evaluation of Coated Foils	2
III. Slitting	2
IV. Termination	4
V. Encapsulation	4
VI. Life Testing	5
VII. Sample Capacitors	5
A. Coated Foil Data	7
B. Construction Information	7
C. Dissipation Factor Shift with Temperature	10
Appendix - ML-1 Capacitors - Quality Control Test - Development Phase	11
Test Summary - Table VI	13

TABLE OF CONTENTS

(Continued)

	<u>Page</u>
Figure 1	3
Figure 2	6
Figure 3	8
Figure 4	9
Figure 5	12
Table I	2
Table II	4
Table III	5
Table IV	7
Table V	10
Table VI	13-27

I. Substrate Preparation

The first phase of the study to improve the surface of the aluminum substrate has been initiated. The areas in which active work has been done include:

- A. Surface Decontamination
- B. Mechanical Smoothing
- C. Electrochemical Polishing

The processing of foils for surface decontamination has been carried out using a makeshift machine since the machine designed for this operation was not available until December 20, 1963.

A. Surface Decontamination

Special aluminum foils have been obtained 0.0006" thick x 1" wide both sides bright for these trials. These foils have been cleaned using trichloroethylene baths. The cleaning conditions were as follows:

1. One pass bath at approximately 1 ft/min foil speed.
2. Two pass bath at approximately 1 ft/min foil speed.
3. One pass bath at approximately 1/2 ft/min foil speed.

The foil speed through the bath was not constant since the machine used operated at fixed winding spool speeds. All operations were performed at room temperature (71-74°F). The trichloroethylene was air dried as the foil was rewound. The quantities cleaned in each manner were limited to 200 feet due to rewind difficulties with the processing machine.

The cleaned foils have been shipped to the Union Carbide Plastics Division to be coated with ML-1 film approximately 2 μ thick. The coated foils will be evaluated electrically and made into roll capacitors for comparative testing.

The new foil handling machine has been checked to determine its capability to rewind large rolls of foil and has been found satisfactory.

B. Mechanical Smoothing

A manufacturer has been located that has a special rolling mill which is claimed to be capable of producing 0.00025" thick aluminum foil bright on both sides. Arrangements have been made to make trial runs on this rolling mill early in January. The surface roughness of the resulting foils will be determined and compared to presently available foils.

C. Electrochemical Polishing

Aluminum foils of special electrolytic grades and purities have been ordered and processing will begin as soon as the new foil handling machine is equipped with chemical resistant guide rollers.

II. Evaluation of Coated Foils

Foils No. 10-17 and 10-18 were purchased for this contract and were used to assemble capacitors for evaluation (Batch USN-1). These foils (440 ft total) were 0.00025" thick x 1" wide before coating. The thickness and breakdown voltage of the foils were measured on the equipment described in the First Quarter Progress Report. The test methods were standardized as a raw material quality control test (see Appendix).

III. Slitting

Slitting of ML-1 coated foils has been carried out at Hamilton Watch Company. A search is still under way for a manufacturer to supply a slitting machine adequate for this material.


Coated foils have been slit to 1/4, 1/2, 3/4, 1-1/4 and 1-1/2" from 1" or 2" stock. The capacitors rolled from the slit foils exhibited the same electrical properties and failure rates as capacitors rolled from 1" wide unslit stock when these slit edges were placed in the margin of the roll (see Figure 1).

A difference in voltage breakdown was anticipated when the slit edges were placed inside the roll as seen in Figure 1. This is based on the reduction of dielectric thickness in the area of the slit edge. Experimental results on capacitors made with one and two slit edges in the roll gave the yields shown in Table I when tested at 140 VDC at room temperature.

TABLE I

	Control	One Slit Edge in Roll	Two Slit Edges in Roll
Trial 1	80%	45%	0%
Trial 2	84%	61%	40%

FIGURE 1

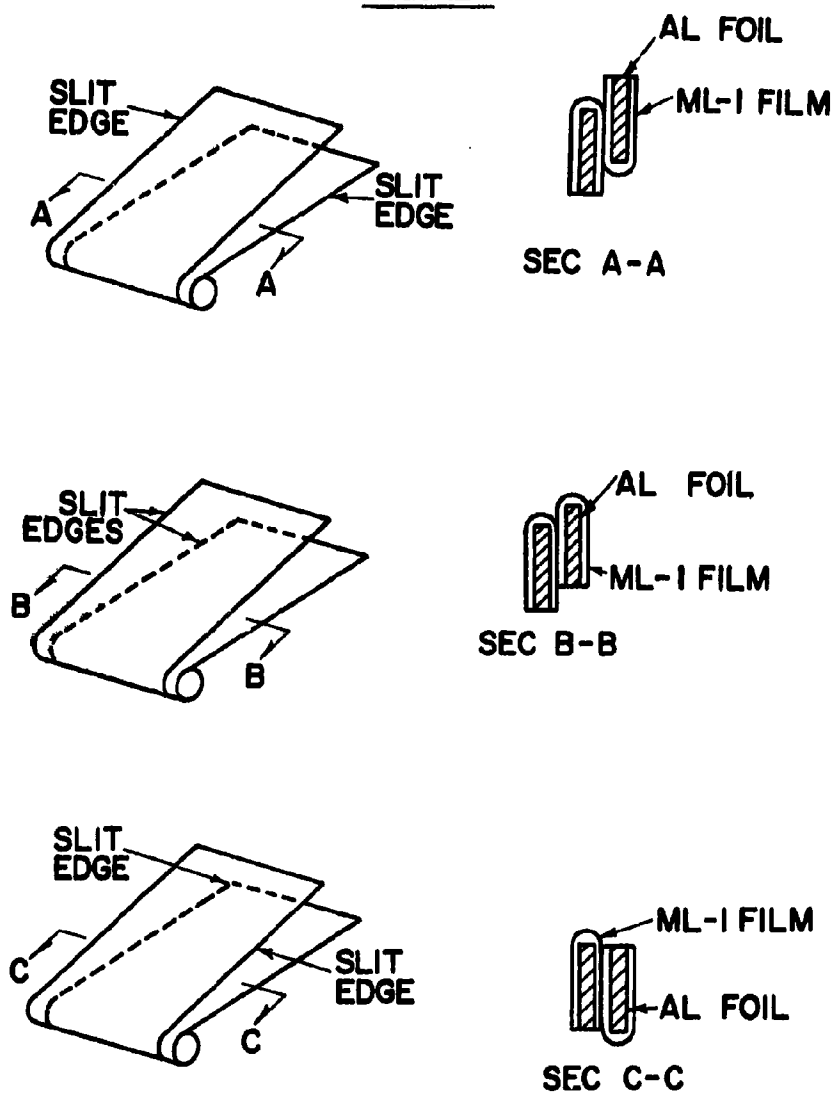

From these data it is conclusive that slit edges of coated foil must not be rolled in the capacitor. Methods are being investigated to remove the exposed aluminum at the slit edge which would permit better material utilization by multiple slitting. The preliminary parts from these tests are now on life test at 50 volts and 170°C.

IV. Termination

The termination of the capacitor rolls by flame spraying and soldering was not considered adequate since some of the parts sprayed did not attain sufficient bond strength on one end to withstand handling. Tensile tests indicated 3-4 pounds of bond strength after soldering the lead. By proper grinding with 80 grit abrasive and improved control of the flame spray, the bond strength was increased to 12 pounds minimum measured by the same tensile test. The solderability also remained very good. The melting point of the solder has been increased from 60/40 alloy (183°C melting point) to 95% tin-5% antimony (232°C melting point). With these changes the processing problems at termination have been eliminated.

Vibration tests were made to check the mechanical stability of the capacitors. Capacitors were subjected to loads of 15 and 30 g for 8 hours at a frequency of 5 to 2000 cps and also a 50 g, 11 milliseconds shock test. No failures occurred during or as a result of these tests.

V. Encapsulation

The capacitors are hermetically sealed in nickel-silver cans (65% copper-17% zinc-18% nickel). New cans are being made in the sizes shown in Table II; delivery will be complete by the end of January on all sizes.

TABLE II

<u>L</u>	<u>OD</u>	<u>ID</u>
0.750	0.195	0.175
0.750	0.240	0.220
1.000	0.290	0.270
1.000	0.345	0.325
1.250	0.398	0.378
1.500	0.398	0.378
1.750	0.398	0.378

As these cans become available, capacitors of other microfarad ratings will be made.

VI. Life Testing

ML-1 capacitors have been life tested at temperatures of 125 and 170°C and voltages of 50, 70, and 100 volts. A failure detection system is used which automatically indicates time of failure and panel identification. This is done without disturbance to other units or interruption of the test. From the panel identification code, test conditions and elapsed time to failure can be determined. A schematic of the system is shown in Figure 2. A test panel for one test condition, i.e., 50 volts, 170°C, has 45 test capacitor positions with series diodes and a common SCR triggering circuit which actuates the clock printer. By multiplexing the six code characters of the printer, individual identification of more than 50 panels (2,250 pcs) is possible.

The main objective of the life testing done to date has been the evaluation of many material, design and processing parameters rather than to establish the failure rate of a large number of capacitors of similar genesis.

VII. Sample Capacitors

Capacitors were constructed from coated foils 10-16 and 10-17 using the best methods available to date. The detailed Construction Information section (Item B) outlines these methods. Electrical measurements have been made on these parts and life tests started at 50 VDC and 170°C.

A summary of average electrical values is shown in the following table:

TABLE III

Cap. - μ f at 1 KC	DF - % 1 KC	DA* %	IR at 170°C megohm- μ f	TCC - ppm/°C		
				-55	+85	+150
0.1083	0.014	0.082	1.3×10^2	-126	-59	-63

* Dielectric Absorption

For detailed measurements on each capacitor see appended Table VI.



A. Coated Foil Data

TABLE IV

Foil No.	Thickness		Breakdown Volts	
	Bright	Dull	Bright	Dull
10-16	2.22 μ	2.17 μ	160-650 (417 avg.)	250-800 (596 avg.)
10-17	2.25 μ	2.17 μ	300-600 (519 avg.)	150-920 (507 avg.)

See Figures 3 and 4.

B. Construction Information

Batch No. USN-1	No. 10-16 & No. 10-17
Foils Used:	(See Foil Testing Sheet)
Breakdown Voltage Foil:	500 Volts Average (See Foil Testing Sheet)
Coating Thickness:	2.2 μ - Average from Foil Testing Sheet
Foil Width:	1"
Target Capacitance:	0.10 μ f
Pieces Rolled:	116
Arbor Size:	0.060"
Encapsulant:	Dow Corning Sylgard 183
Tape:	Teflon 3M No. 69
Solder:	95% Tin-5% Antimony
Processing Losses After:	
Rolling	0
Grinding	2
Flame Spray	0
Lead Attach.	0
Canning	0
Voltage	0
Conditioning	2 - See Note

Note: Conditioning losses were due to loss of terminations. Parts were opened leads attached and reassembled. These parts are included in the data as Nos. 15 and 54.

Note: Roll Size - 0.170 O.D. x 1.10" Long
Can Size - 0.290 x 1.50" Long
Oversized can used as a matter of availability.

FIGURE 3

VAPOR-DEPOSITED PARYLENE FILM


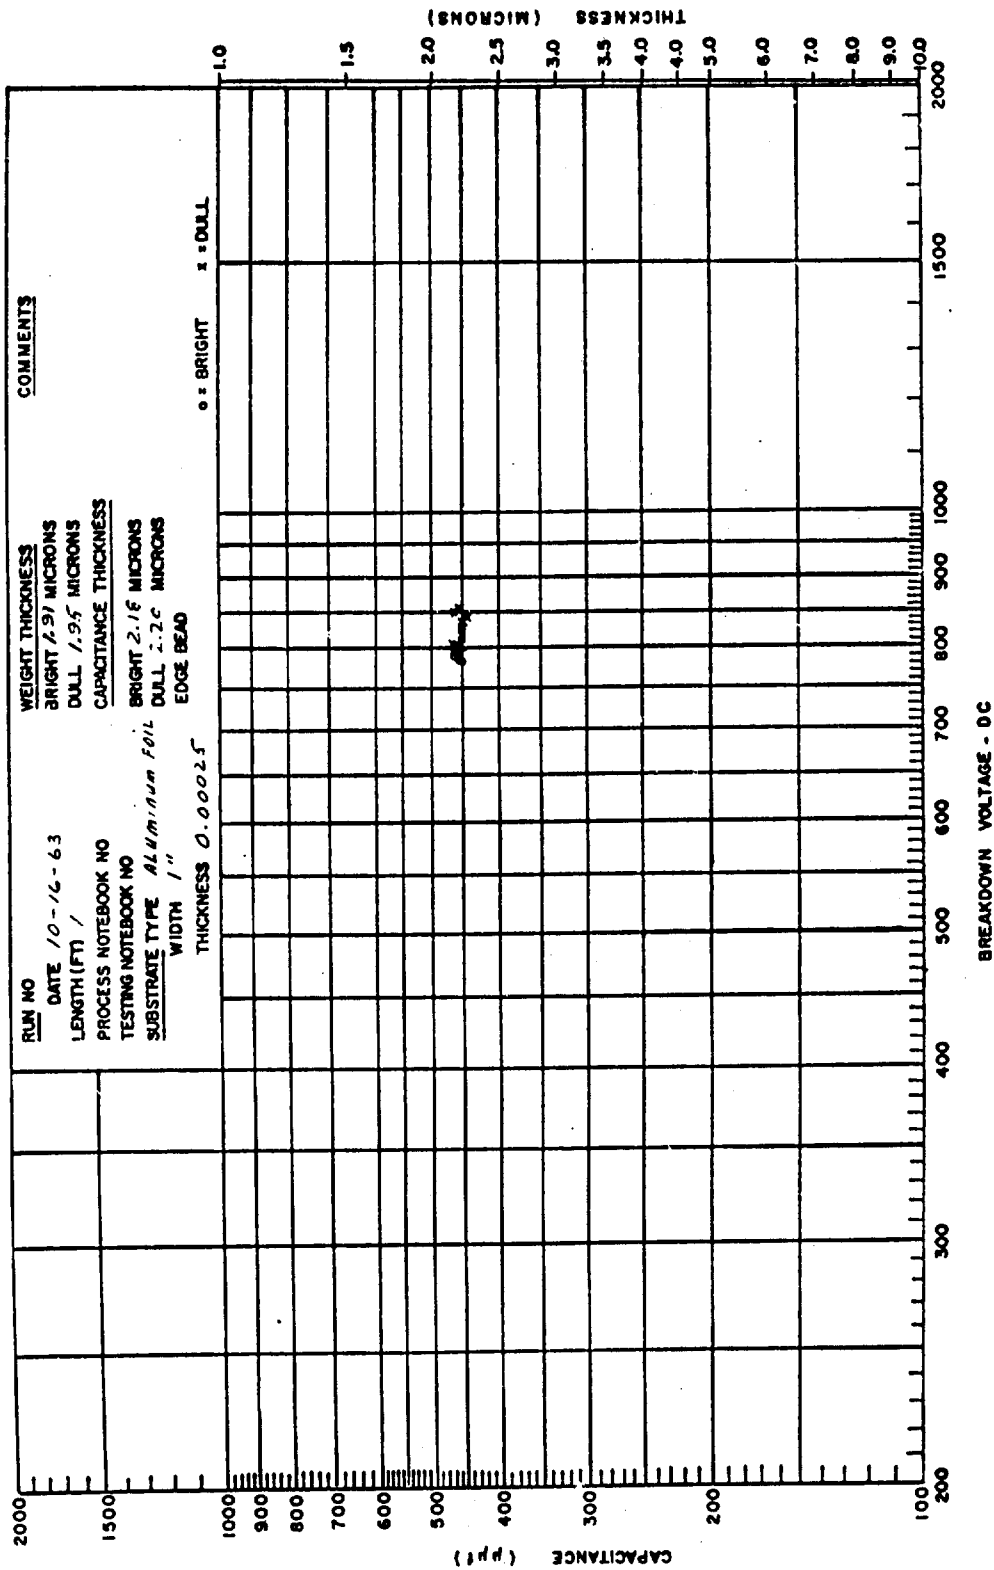


FIGURE 4

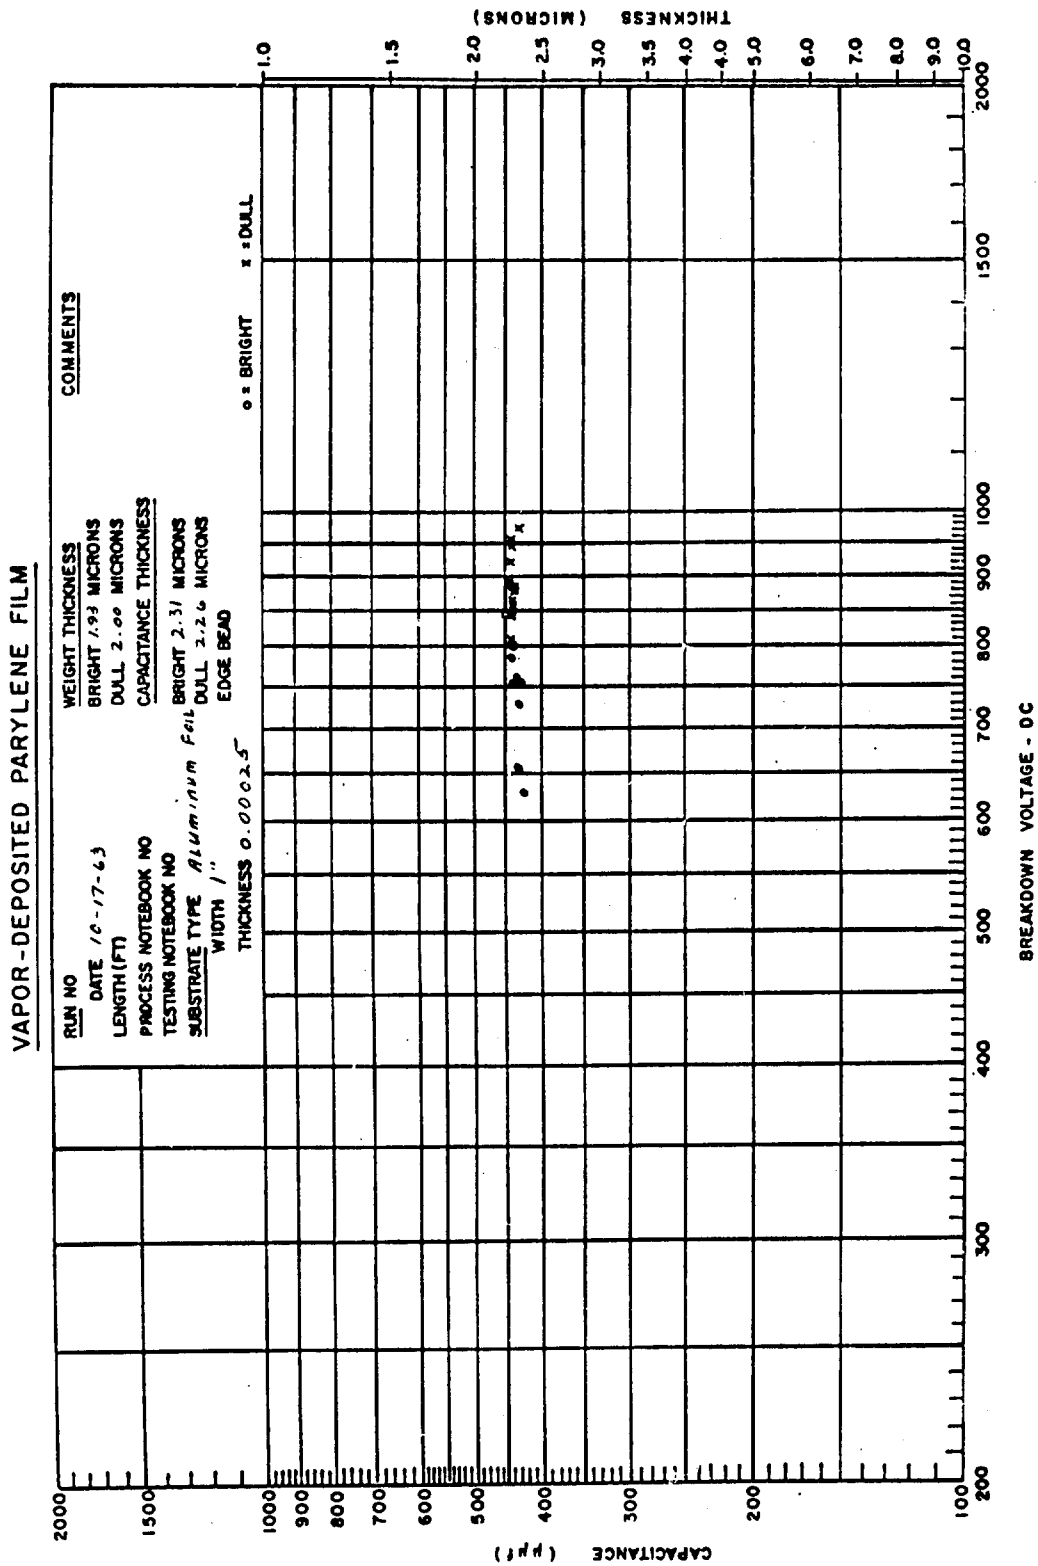

C. Dissipation Factor Shift with Temperature

A new piece of apparatus has been constructed to test dissipation factor at various temperatures. This apparatus is comprised of a temperature test chamber which is connected to a General Radio bridge Model 716A using 1/4" bus bar less than one foot long to obtain low lead resistance. The dissipation factors measured on this apparatus were found to be identical with the values obtained when connected directly to the bridge. Representative dissipation factors measured over the temperature range of -195°C (liquid N₂) to +170°C are shown in the following table:

TABLE V

Dissipation (%) Measured at 1 KC				
-196°C	-55°C	25°C	150°C	170°C
0.011	0.034	0.011	0.018	0.025

The improved apparatus described here makes possible much higher accuracy than previously obtained. The results indicate only minor changes in dissipation factor over the temperature range used.

APPENDIX

ML-1 Capacitors - Quality Control Test - Development Phase

Equipment

- (a) Ballantine Capacitance Meter Model 520
- (b) Microdot BDV Tester Model 1901-A
- (c) Test Fixture
- (d) Mercury Probe

Materials

- (a) Coated Foil Stock
- (b) Clean Mercury

QC Instructions ML-1 Coated Aluminum Foil

- 1. Each roll of coated foil shall be sampled and checked for coating thickness and breakdown voltage on both sides.
- 2. The sample shall consist of 12" to 14" of coated stock which is free from wrinkles and creases.
- 3. Procedure -

The sample shall be laid across a smooth glass or lucite block and a calibrated electrode (see attached figure) placed on the surface and filled to the top with mercury. A small area at the end of the foil shall be bared by peeling away the ML-1 coating and electrical connection made at this point. The Microdot breakdown voltage tester shall be connected between the bared foil and the mercury electrode. Three BDV measurements shall be made at each test spot using a 10 μ a current limit. The Microdot tester shall then be disconnected and the capacitance measured by connecting the Ballantine capacitance meter between the bared foil and the calibrated mercury electrode. The Microdot tester shall then be reconnected and the BDV measured using the 1 ma current limit. Three BDV measurements shall be made at each test spot using 1 ma current limit. The highest value at 1 μ a and 1 ma current limits shall be recorded as BDV for each test spot.


At least six such measurements shall be made on each side of the sample. A range and average shall be determined for capacitance and BDV on each side. The coating thickness shall be determined from the capacitance measurement by using the formula

$$\frac{1000}{pf} = \text{film thickness in microns.}$$

When moving the mercury electrode from one test area to another it shall be lifted off the foil surface to prevent damage to the coating and false readings.

FIGURE 5

MERCURY ELECTRODE CELL

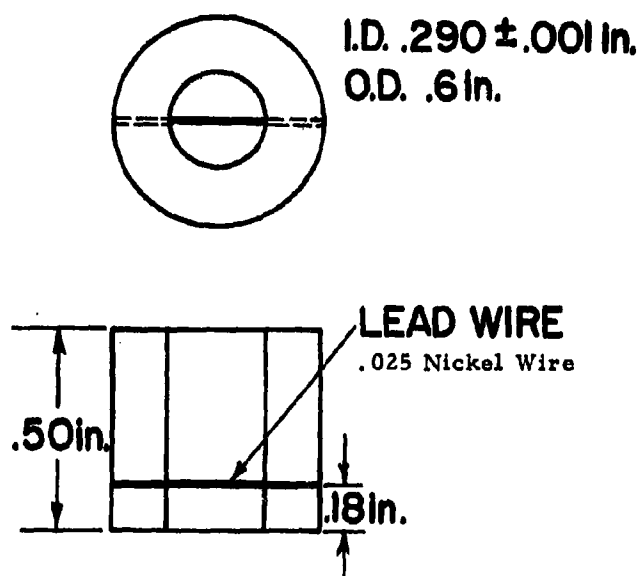

Material - Lucite

Polish Bottom - Break Edge

TABLE VI
TEST SUMMARY
BATCH: USN-1

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC	-55°	+85°	+150°	140 VDC 2 Min. Voltage	170 °C IR Megohms	% D. A.
Loss on Grinding										
1	0 250 500 1000									
	0	.10136	.02	-116	-50	-57	-	x	1.17×10^3	-
	250	.10350	.02	-	-	-	-	-	1.6×10^2	-
2	500 1000									
	0	.10208	.01	-126	-56	-52	-	x	1.60×10^3	-
	250	.10440	.02	-	-	-	-	-	2.0×10^2	-
3	500 1000									
	0	.10456	.012	-131	-54	-50	-	x	2.0×10^1	-
4	250 500 1000									
	0	.11119	.012	-135	+15	-62	-	x	1.3×10^3	.071
	250	.11336	.02	-125	-52	-90	-	-	1.3×10^3	.124
5	500 1000									
	0	.11028	.075	-128	-64	-65	-	x	9.8×10^2	-
	250	.11256	.02	-	-	-	-	-	4.1×10^2	-
6	500 1000									
	0	.11619	.01	-130	-80	-67	-	x	1.02×10^3	-
	250	.1178	.02	-	-	-	-	-	1.3×10^3	-
7	500 1000									

x = Passed 140 V, 2 Min. Test D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	TCC		140 VDC 2 Min. Voltage	170°C IR Megohms	% D.A.
			- 55°	+85°			
8	0	.10694	.015	-46	x	2.5 x 10 ³	-
	250	.10892	.02	-	-	3.8 x 10 ³	-
	500						
	1000						
9	0	.10071	.01	-133	-49	-53	-
	250	.10332	.02	-	-	-	-
	500						
	1000						
10	0	.11097	.02	-129	-67	-64	-
	250	.11840	.085	-	-	-	-
	500						
	1000						
11	0	.10926	.01	-133	-80	-97	-
	250	.11084	.02	-	-	-	-
	500						
	1000						
12	0	.10886	.022	-137	-59	-74	-
	250	Short at 250 Hours L. T.					
	500						
	1000						
13	0	.10764	.015	-127	-55	-48	Open
	250	Not on L. T. Due to Open					
	500						
	1000						
14	0	.10893	.015	-105	-52	-42	2.5 x 10 ³
	250	.11119	.02	-	-	-	7.3 x 10 ²
	500						
	1000						

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage		170 °C IR Megohms		% D.A.
				- 55°	+85°	+150°	SHT	SHT	SHT	
15	0	.10865	.012	- 56	-09	+ 26				
	250	Not on L. T.	Due to Short							
	500									
	1000									
16	0	.1155	.012	-130	-27	- 58	x	1.4 x 10 ³		.076
	250	.1176	.04	-134	-68	-105	-	5.2 x 10 ²		.090
	500									
	1000									
17	0	.11383	.01	-142	-78	- 42	x	9.8 x 10 ²		
	250	.1158	.025	-	-	-	-	2.5 x 10 ²		
	500									
	1000									
18	0	.10226	.012	-113	-45	- 03	x	2.5 x 10 ³		.138
	250	Short at 250 Hours	L. T.							
	500									
	1000									
19	0	.10568	.01	-145	-58	- 12	x	3.75 x 10 ³		.077
	250	.10778	.075	-146	+ 5	- 59	-	3.5 x 10 ³		.073
	500									
	1000									
20	0	.10496	.01	-140	-78	- 48	x	Open		Open
	250	Not on L. T.	- Open							
	500									
	1000									
21	0	.10366	.01	-131	-60	0	x	4.5 x 10 ³		.102
	250	.10602	.02	-132	- 7	- 58	-	1.0 x 10 ³		
	500									
	1000									
22	0	.11533	.01	-142	-80	- 87	x	7.76 x 10 ²		-
	250	.11720	.02	-	-	-	-	1.0 x 10 ⁴		-
	500									
	1000									
x = Passed 140 V, 2 Min. Test										
										D. A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition	TCC		140 VDC 2 Min. Voltage		170 °C IR		% D.A.
			- 55°	+85°	+150°	x	Megohms	SHT	
23	0	Cap. - µf	- 55°	+85°	+150°	x	2.8 x 10 ²	SHT	-
	250	.11270	-134	-82	- 95				
	500	Short on L. T. at 5 Hours							
	1000								
24	0	.11316	-147	-80	- 29			SHT	SHT
	250	Not on L. T. Due to Short							
	500								
	1000								
25	0	Loss on Grinding							
	250								
	500								
	1000								
26	0	.11276	-148	-81	- 42		2.5 x 10 ³		.107
	250	.1152	-137	-70	-110		7.3 x 10 ²		.073
	500								
	1000								
27	0	.11037	-132	-67	- 34	x	1.6 x 10 ³		.053
	250	.11264	-124	-57	- 95		1.1 x 10 ³		
	500								
	1000								
28	0	.11271	-142	-87	- 50			SHT	SHT
	250	Not on L. T. Due to Short							
	500								
	1000								
29	0	.10408	-135	-57	- 10	x	1.87 x 10 ³		.076
	250	.10626	-117	-29	- 72		1.6 x 10 ³		
	500								
	1000								
30	0	.11050	-138	-56	+ 07	x	1.46 x 10 ³		.080
	250	.11290	-115	-38	- 76		1.0 x 10 ³		
	500								
	1000								

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	TCC		140 VDC 2 Min. Voltage	170°C IR Megohms	% D.A.
			- 55°	+85°			
31	0	.10517	.01	-118	-45	+04	.044
	250	Short on L.T. at 5 Hours			x	1.72 x 10 ³	
	500						
	1000						
32	0	.10589	.01	-137	-64	-17	-
	250	.10857	.02	-130	-44	-89	
	500						
	1000						
33	0	.10462	.012	-109	-45	-83	Open
	250	.10990	.105	-46	+68	+40	
	500						
	1000						
34	0	.10518	.01	-117	-35	-67	-
	250	.10706	.02	-	-	-	
	500						
	1000						
35	0	.11430	.01	-138	-88	-114	-
	250	.11640	.02	-	-	-	
	500						
	1000						
36	0	.10668	.017	-107	-49	-80	-
	250	.10842	.02	-	-	-	
	500						
	1000						
37	0	.10671	.012	-120	-64	-92	-
	250	Short on L.T. at 5 Hours			x	1.02 x 10 ³	
	500						
	1000						
38	0	.1176	.015	-140	-90	-115	-
	250	.12110	.03	-	-	-	
	500						
	1000						

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	TCC			140 VDC 2 Min. Voltage	170°C IR		% D.A.
			- 55°	+85°	+150°		Megohms		
39	0	.11012	-132	-72	-84	x	6.6×10^2		-
	250	.11222	-	-	-	-	1.07×10^2		-
	500								
	1000								
40	0	.11200	-133	-78	-102	x	1.87×10^3		-
	250	.11394	-	-	-	-	2.7×10^2		-
	500								
	1000								
41	0	.11341	-123	-77	-108	x	8.3×10^2		-
	250	.11580	-	-	-	-	7.0×10^2		-
	500								
	1000								
42	0	.10836	-105	+40	-67	x	1.55×10^3		-
	250	.11013	-	-	-	-	3.2×10^2		-
	500								
	1000								
43	0	.1191	-125	-95	-135	x	3.75×10^2		-
	250	Short at 250 Hours L.T.							
	500								
	1000								
44	0	.11288	-	-	-	x	7.76×10^2		-
	250	.11520	-	-	-	-	3.5×10^2		-
	500								
	1000								
45	0	.10747	-104	-39	-64	x	2.8×10^3		-
	250	.10916	-	-	-	-	1.1×10^3		-
	500								
	1000								
46	0	.10676	-	-	-	x	6.4×10^2		-
	250	.10815	-	-	-	-	3.2×10^2		-
	500								
	1000								
x = Passed 140 V, 2 Min. Test							D.A. = Dielectric Absorption		

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
66
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
84

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage	170 °C IR Megohms	% D.A.
				- 55°	+85°			
47	0	.10304	.015	-109	-45	x	4.1 x 10 ³	-
	250	.11680	.110	-	-	-	6.5 x 10 ²	-
	500							
	1000							
48	0	.1221	.02	-	-	x	1.4 x 10 ³	-
	250	.1234	.025	-	-	-	4.5 x 10 ²	-
	500							
	1000							
49	0	.10358	.018	-	-	x	Open	Open
	250	Not on L. T. due to Open						
	500							
	1000							
50	0	.10091	.015	-	-	x	8.0 x 10 ²	-
	250	.10197	.025	-	-	-	3.8 x 10 ²	-
	500							
	1000							
51	0	.11238	.01	-127	-16	x	Open	Open
	250	Not on L. T. due to Open						
	500							
	1000							
52	0	.10448	.01	-133	+16	x	1.72 x 10 ³	-
	250	.10707	.02	-	-	-	9.8 x 10 ²	-
	500							
	1000							
53	0	.10300	.01	-138	-63	x	3.75 x 10 ³	-
	250	.11780	.11	-	-	-	1.6 x 10 ²	-
	500							
	1000							
54	0	.10652	.01	-	-	x	5.1 x 10 ²	-
	250	.10876	.02	-	-	-	8.7 x 10 ¹	-
	500							
	1000							

x = Passed 140 V, 2 Min. Test D.A. = Dielectric Absorption

1. The first step is to identify the key components of the system. This involves understanding the hardware, software, and data involved. 2. The second step is to define the requirements. This includes determining the functional requirements, performance requirements, and security requirements. 3. The third step is to design the system. This involves creating a detailed architecture and specifying the components and their interactions. 4. The fourth step is to implement the system. This involves writing the code, configuring the hardware, and testing the system. 5. The fifth step is to maintain the system. This involves monitoring the system for performance, security, and availability, and making updates as needed.

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.		TCC		140 VDC 2 Min. Voltage	170°C IR Megohms	% D.A.
			- 55°	- 89	+85°	+150°			
55	0	.10519	.01	- 89	-40	- 73	x	3.75 x 10 ³	-
	250	.10654	.02	-	-	-	-	1.1 x 10 ³	-
	500								
	1000								
56	0	.11256	.012	-	-	-	x	2.25 x 10 ³	-
	250	Short on L. T. at 5 Hours							
	500								
	1000								
57	0	.1159	.01	-140	-94	-140	x	1.25 x 10 ³	-
	250	.1210	.055	-	-	-	-	2.1 x 10 ³	-
	500								
	1000								
58	0	.10721	.015	-	-	-	x	2.4 x 10 ³	-
	250	.10859	.025	-	-	-	-	6.6 x 10 ²	-
	500								
	1000								
59	0	.11046	.015	-	-	-	x	3.0 x 10 ²	-
	250	.11280	.04	-	-	-	-	3.2 x 10 ²	-
	500								
	1000								
60	0	.10620	.015	-	-	-	x	1.72 x 10 ³	-
	250	.10892	.03	-	-	-	-	1.6 x 10 ³	-
	500								
	1000								
61	0	.1148	.018	-	-	-	x	1.6 x 10 ³	-
	250	.11660	.02	-	-	-	-	7.3 x 10 ²	-
	500								
	1000								
62	0	.11245	.012	-	-	-	x	1.46 x 10 ³	-
	250	.11348	.02	-	-	-	-	1.3 x 10 ³	-
	500								
	1000								

x = Passed 140 V, 2 Min. Test D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage	170°C IR Megohms	% D.A.
				- 55°	+85°			
63	0	.11002	.01	-	-	x	1.3×10^3	-
	250	.11097	.02	-	-	-	1.3×10^3	-
	500							
	1000							
64	0	.1151	.018	-	-	x	7.0×10^2	-
	250	Short at 250 Hours L.T.						
	500							
	1000							
65	0	.1168	.018	-	-	x	6.3×10^2	-
	250	.11780	.022	-	-	-	8.0×10^2	-
	500							
	1000							
66	0	.1168	.018	-	-	x	1.02×10^3	-
	250	.1258	.090	-	-	-	1.5×10^2	-
	500							
	1000							
67	0	.1176	.018	-	-	x	7.0×10^2	-
	250	.1194	.020	-	-	-	5.1×10^2	-
	500							
	1000							
68	0	.11257	.01	-	-	x	9.2×10^2	-
	250	.11464	.018	-	-	-	7.0×10^2	-
	500							
	1000							
69	0	.11279	.01	-	-	x	5.2×10^2	-
	250	.11492	.02	-	-	-	1.7×10^3	-
	500							
	1000							
70	0	.10767	.01	-	-	x	3.75×10^3	-
	250	.10923	.02	-	-	-	5.6×10^2	-
	500							
	1000							
x = Passed 140 V, 2 Min. Test								D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC			140 VDC 2 Min. Voltage	170°C IR		% D.A.
				- 55°	+85°	+150°		Megohms	IR	
71	0	.10402	.010	-	-	-	x	1.96 x 10 ³	-	-
	250	.10506	.02	-	-	-	-	7.5 x 10 ²	-	-
	500									
	1000									
72	0	.10423	.012	-	-	-	x	2.4 x 10 ³	-	-
	250	.10620	.02	-	-	-	-	8.3 x 10 ²	-	-
	500									
	1000									
73	0	.10904	.012	-	-	-	x	8.0 x 10 ²	-	-
	250	.10997	.022	-	-	-	-	6.2 x 10 ¹	-	-
	500									
	1000									
74	0	.10536	.012	-	-	-	x	1.3 x 10 ³	-	-
	250	.10648	.02	-	-	-	-	3.8 x 10 ²	-	-
	500									
	1000									
75	0	.10230	.012	-	-	-	x	8.7 x 10 ²	-	-
	250	.10358	.02	-	-	-	-	2.3 x 10 ²	-	-
	500									
	1000									
76	0	.11287	.01	-	-	-	x	6.2 x 10 ²	-	-
	250	.11492	.018	-	-	-	-	2.7 x 10 ³	-	-
	500									
	1000									
77	0	.10827	.015	-	-	-	x	4.9 x 10 ²	-	-
	250	.10984	.022	-	-	-	-	7.0 x 10 ²	-	-
	500									
	1000									
78	0	.10601	.012	-	-	-	x	6.4 x 10 ²	-	-
	250	.11206	.015	-	-	-	-	7.5 x 10 ²	-	-
	500									
	1000									
x = Passed 140 V, 2 Min. Test										D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	TCC		140 VDC 2 Min. Voltage	170°C IR Megohms	% D.A.
			- 55°	+85°			
79	0	.10661	.015	-	x	6.2×10^2	-
	250	.10754	.02	-	-	2.7×10^2	-
	500						
	1000						
80	0	.10918	.01	-	x	3.2×10^3	-
	250	.11054	.02	-	-	1.5×10^3	-
	500						
	1000						
81	0	.10341	.01	-	x	1.5×10^3	-
	250	.10452	.03	-	-	3.8×10^1	-
	500						
	1000						
82	0	.11062	.012	-	x	5.4×10^2	-
	250	.11202	.02	-	-	6.7×10^2	-
	500						
	1000						
83	0	.10200	.01	-	x	1.96×10^3	-
	250	.10330	.02	-	-	4.1×10^2	-
	500						
	1000						
84	0	.10552	.012	-	x	4.7×10^2	-
	250	.10649	.03	-	-	2.3×10^2	-
	500						
	1000						
85	0	.11030	.012	-	x	4.8×10^2	-
	250	.11110	.02	-	-	2.5×10^2	-
	500						
	1000						
86	0	.10904	.012	-	x	7.0×10^2	-
	250	.11017	.02	-	-	8.3×10^2	-
	500						
	1000						

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	TCC		140 VDC 2 Min. Voltage	170 °C IR		% D.A.
			- 55°	+85°		Megohms	IR	
87	0	.10471	-	-	x	5.6 x 10 ²	-	-
	250	.10588	-	-	-	5.1 x 10 ²	-	-
	500							
	1000							
88	0	.10856	-	-	x	1.17 x 10 ³	-	-
	250	.10980	-	-	-	2.8 x 10 ²	-	-
	500							
	1000							
89	0	.10570	-	-	x	Open	Open	-
	250	Not on L. T. due to Open						
	500							
	1000							
90	0	.10839	-	-	x	8.0 x 10 ²	-	-
	250	.10940	-	-	-	1.6 x 10 ³	-	-
	500							
	1000							
91	0	.11238	-	-	x	1.7 x 10 ³	-	-
	250	.11323	-	-	-	4.1 x 10 ²	-	-
	500							
	1000							
92	0	.10231	-	-	x	1.3 x 10 ³	-	-
	250	.10351	-	-	-	1.1 x 10 ³	-	-
	500							
	1000							
93	0	.11273	-	-	x	1.3 x 10 ²	-	-
	250	Short on L. T. at 5 Hours						
	500							
	1000							
94	0	.11206	-	-	x	5.6 x 10 ²	-	-
	250	.11324	-	-	-	2.0 x 10 ²	-	-
	500							
	1000							

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage	170°C IR		% D.A.
				- 55°	+85°		Megohms	IR	
95	0	.10543	.012	-	-	x	7.4 x 10 ²	-	-
	250	.10637	.020	-	-	-	1.7 x 10 ²	-	-
	500								
	1000								
96	0	.11018	.012	-	-	x	1.7 x 10 ³	-	-
	250	.11181	.022	-	-	-	7.0 x 10 ²	-	-
	500								
	1000								
97	0	.10858	.015	-	-	x	1.6 x 10 ³	-	-
	250	.10990	.022	-	-	-	1.9 x 10 ³	-	-
	500								
	1000								
98	0	.10558	.01	-	-	x	1.7 x 10 ³	-	-
	250	.10748	.021	-	-	-	6.3 x 10 ²	-	-
	500								
	1000								
99	0	.10756	.175	-	-	SHT	SHT	SHT	SHT
	250	Not on L. T. due to Short							
	500								
	1000								
100	0	.11059	.013	-	-	x	1.3 x 10 ³	-	-
	250	.11169	.020	-	-	-	1.8 x 10 ³	-	-
	500								
	1000								
101	0	.10960	.01	-	-	x	6.4 x 10 ²	-	-
	250	Not on L. T.							
	500								
	1000								
102	0	.10738	.01	-	-	x	1.25 x 10 ³	-	-
	250	Not on L. T.							
	500								
	1000								

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage	170 °C IR Megohms	% D.A.
				- 55 °	+85 °			
103	0	.10174	.01	-	-	x	1.25 x 10 ³	-
	250	Not on L. T.						
	500							
	1000							
104	0	.10480	.01	-	-	x	8.8 x 10 ²	-
	250	Not on L. T.						
	500							
	1000							
105	0	.11196	.012	-	-	x	1.4 x 10 ²	-
	250	Not on L. T.						
	500							
	1000							
106	0	.09835	.013	-	-	x	1.87 x 10 ²	-
	250	Not on L. T.						
	500							
	1000							
107	0	.10087	.01	-	-	x	3.2 x 10 ²	-
	250	Not on L. T.						
	500							
	1000							
108	0	.09849	.012	-	-	x	1.3 x 10 ³	-
	250	Not on L. T.						
	500							
	1000							
109	0	.10029	.01	-	-	x	1.13 x 10 ³	-
	250	Not on L. T.						
	500							
	1000							
110	0	.09860	.01	-	-	x	8.5 x 10 ²	-
	250	Not on L. T.						
	500							
	1000							

x = Passed 140 V, 2 Min. Test

D.A. = Dielectric Absorption

TEST SUMMARY (Continued)

No.	Life Test Hours	After Condition Cap. - μ f	% Dis.	TCC		140 VDC 2 Min. Voltage	170 °C. IR Megohms	% D.A.
				- 55°	+85°			
111	0	.09099	.01	-	-	x	1.2 x 10 ³	-
	250	Not on L.T.						
	500							
	1000							
112	0	.09104	.012	-	-	x	9.8 x 10 ²	-
	250	Not on L.T.						
	500							
	1000							
113	0	.09735	.01	-	-	x	1.5 x 10 ³	-
	250	Not on L.T.						
	500							
	1000							
114	0	.10204	.01	-	-	x	1.02 x 10 ²	-
	250	Not on L.T.						
	500							
	1000							
115	0	.1401	.02	-	-	SHT	SHT	SHT
	250	Not on L.T.						
	500							
	1000							
116	0	.1206	.02	-	-	x	2.8 x 10 ²	-
	250	.1220	.03	-	-	-	1.0 x 10 ³	-
	500							
	1000							
x = Passed 140 V, 2 Min. Test								
Arithmetic Average				D.A. = Dielectric Absorption				
0	.10833	.014	48/126	48/59	48/63*	104/1.3 x 10 ⁴	10/.082	
250	80/.11133	.029	10/121	10/44	10/79	80/9.4 x 10 ²		
500								
1000								

* Pieces Measured/ppm/°C

Distribution List for Reports Issued under Contract NObsr-89519

<u>Addressee</u>	<u>No. of Copies</u>
Chief, Bureau of Ships Department of the Navy Washington, D. C. 20360 Attention: Code 681A2	2
Chief, Bureau of Ships Department of the Navy Washington, D. C. 20360 Attention: Code 210L	3
Chief, Bureau of Naval Weapons Department of the Navy Washington, D. C. 20360 Attention: Code RAAV 4123	1
Commanding Officer & Director U. S. Naval Applied Science Laboratory U. S. Naval Base Brooklyn, New York 11251 Attention: Technical Library	1
Commanding Officer & Director U. S. Naval Applied Science Laboratory U. S. Naval Base Brooklyn, New York 11251 Attention: Mr. H. M. Strobel, Code 9230	1
Commanding Officer U. S. Naval Ordnance Laboratory Corona, California Attention: H. H. Wieder, Code RRMD	1
Commanding Officer U. S. Naval Ordnance Laboratory Corona, California Attention: Technical Library	1
Commander U. S. Naval Ordnance Laboratory White Oak, Silver Spring, Maryland Attention: Technical Library	1
Director U. S. Naval Research Laboratory Washington, D. C. 20390 Attention: Technical Library	1

<u>Addressee</u>	<u>No. of Copies</u>
Commanding Officer and Director U. S. Navy Underwater Sound Laboratory Fort Trumbull, New London, Conn. Attention: Technical Library	1
Commanding Officer and Director U. S. Navy Electronics Laboratory San Diego 52, California Attention: Mr. R. B. Jordan	1
Commanding Officer U. S. Naval Avionics Facility Indianapolis 18, Indiana Attention: Technical Library	1
Commanding Officer U. S. Naval Avionics Facility Indianapolis 18, Indiana Attention: Noel Scott	1
Commanding General U. S. Army Signal Research and Development Lab. Attention: SIGRA/SL-PEP, Mr. T. S. Gore, Jr. Fort Monmouth, New Jersey	2
U. S. Army Signal Supply Agency 225 South 18th Street Attention: SIGSU-R2A, Mr. I. Azoff Philadelphia 3, Pennsylvania	1
Commander Army Ballistic Missile Agency Attention: Mr. K. W. Plunkett, ORDAB-RG Redstone Arsenal, Alabama	1
Commanding Officer Frankford Arsenal U. S. Army Ordnance Attention: Mr. S. Torrey, CC1742 R&D Gp. Philadelphia 37, Pa.	1
Commanding Officer Harry Diamond Laboratories Attention: Mr. R. W. Tucker Connecticut & Van Ness Streets, N.W. Washington, D. C. 20390	1

<u>Addressee</u>	<u>No. of Copies</u>
Office of the Chief Signal Officer Department of the Army Washington, D. C. 20390 Attention: Mr. W. L. Womack	1
Commander Aeronautical Systems Division Attention: Mr. C. K. Greene, ASRNE Wright-Patterson Air Force Base, Ohio	1
NASA Headquarters Office of Reliability and Quality Assurance Attention: Mr. W. M. Redler 1520 H Street, N. W. Washington, D. C. 20390	1
Dr. W. J. West Autonetics 9150 E. Imperial Highway Downey, California	1
Mr. J. T. Cataldo Hughes Electronics Co. 5271 W. Jefferson Blvd. Los Angeles 16, California	1
Mr. C. G. Killen V.P. of Industrial & Military Sales Sprague Electric Co. North Adams, Massachusetts	1
Advisory Group on Electron Devices 346 Broadway, 8th Floor New York 13, New York	2
Director National Bureau of Standards Washington, D. C. 20390 Attention: Technical Library	1
Headquarters, Defense Documentation Center U. S. Air Force Cameron Station Alexandria, Virginia	20
Scientific and Technical Information Facility P. O. Box 5700 Bethesda, Maryland	2