

UNCLASSIFIED

AD 4 3 7 6 0 6

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED


NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

64-12

437606

Recommended Quality Standards
for Tungsten Sheet
Produced in the
Refractory Metals Sheet Rolling Program

4 3 7 6 0 6

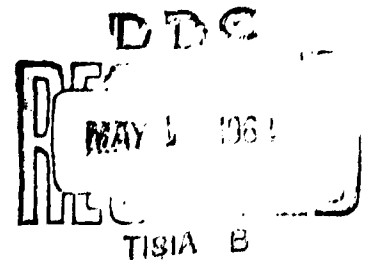

RELEASE TO UTS

**National Academy of Sciences—
National Research Council
Washington, D. C.**

MATERIALS ADVISORY BOARD
DIVISION OF ENGINEERING AND INDUSTRIAL RESEARCH
NATIONAL ACADEMY OF SCIENCES-NATIONAL RESEARCH COUNCIL

Chairman

Dr. Carl S. Marvel (1964)
Department of Chemistry
The University of Arizona
Tucson, Arizona

Members

Professor John C. Bailar, Jr. (1966)
Department of Chemistry & Engineering
The William Albert Noyes Laboratory
The University of Illinois
Urbana, Illinois

Mr. George C. Deutsch, Chief (1966)
Materials Research Program
National Aeronautics & Space Admin.
Washington, D. C. 20546

Dr. Morris E. Fine (1967)
Department of Materials Science
Northwestern University
Evanston, Illinois

Dr. Walter L. Finlay (1967)
Director of Research
Crucible Steel Company of America
4 Gateway Center
Pittsburgh, Pennsylvania

Dr. C. F. Gibbs (1964)
Manager, Rubber Research
B. F. Goodrich Research Center
Brecksville, Ohio

Dr. Wayne E. Hall (1966)
Assistant Chief Geologist for
Experimental Geology
U. S. Geological Survey
Washington 25, D. C.

Dr. Walter R. Hibbard, Jr. (1966)
Manager, Metallurgy & Ceramics
Research Department
General Electric Company
P. O. Box 1088
Schenectady, New York

Dr. Elliott L. Katz (1964)
Associate Director
Fluid Physics Division
Electro-Optical Systems, Inc.
125 North Vineda Street
Pasadena, California

Dr. John H. Koenig, Director (1965)
School of Ceramics
College of Engineering
Rutgers University
New Brunswick, New Jersey

Mr. Alan V. Levy (1967)
Senior Department Manager
Materials and Fabrication
Solid Rocket Plant
Aerojet-General Corporation
Sacramento, California

Dr. Oscar T. Marzke (1964)
Vice President—Fundamental Research
United States Steel Corporation
525 William Penn Place
Pittsburgh 30, Pennsylvania

Dr. D. J. McPherson, Director (1967)
Materials and Structures Research
Illinois Institute of Technology
Research Institute
10 West 35th Street
Chicago 16, Illinois

Dr. M. Eugene Merchant (1966)
Director of Physical Research
Cincinnati Milling Machine Company
Cincinnati 9, Ohio

Mr. John M. Neff (1965)
Senior Research Scientist
The Martin Company
MP 275; P. O. Box 5837
Orlando, Florida

Dr. Charles G. Overberger (1965)
Head, Department of Chemistry
Polytechnic Institute of Brooklyn
333 Jay Street
Brooklyn 1, New York

Dr. A. J. Phillips (1964)
Vice President and Director of Research
American Smelting & Refining Company
South Plainfield, New Jersey

Dr. Malcolm M. Renfrew, Head (1967)
Department of Physical Sciences
University of Idaho
Moscow, Idaho

Dr. Preston Robinson (1966)
Director—Consultant
Sprague Electric Company
North Adams, Massachusetts

Mr. Milton J. Rudick (1964)
Chief of Space Technology
Vought Astronautics
P. O. Box 6267
Dallas 22, Texas

Mr. J. H. Scaff (1965)
Metallurgical Director
Bell Telephone Laboratories, Inc.
Murrah Hill, New Jersey

Dr. Irl C. Schoonover (1966)
Associate Director
National Bureau of Standards
Washington 25, D. C.

Dr. W. H. Steurer (1965)
General Dynamics/Convair
Department 6
San Diego 12, California

Dr. Gordon K. Teal (1964)
Assistant Vice President and
Technical Director
Texas Instruments, Inc.
International Division
Manton Lane
Bedford, England

Mr. Paul Zinner (1964)
Assistant Director—Programs
U. S. Bureau of Mines
Washington 25, D. C.

NATIONAL ACADEMY OF SCIENCES
NATIONAL RESEARCH COUNCIL

MATERIALS ADVISORY BOARD
OF THE
DIVISION OF ENGINEERING AND INDUSTRIAL RESEARCH

MAILING ADDRESS:
2101 CONSTITUTION AVENUE, N.W.
WASHINGTON 25, D. C.

OFFICES:
1155 16TH STREET, N.W.

January 22, 1964

Dear Sir:

I am forwarding herewith the report entitled "Recommended Quality Standards for Tungsten Sheet Produced in the Refractory Metals Sheet Rolling Program" by the Subpanel on Quality Specifications of the Refractory Metals Sheet Rolling Panel, which has been submitted through the National Academy of Sciences-National Research Council to the Director of Defense, Research and Engineering. This report has been reviewed by the Refractory Metals Sheet Rolling Panel and by individual members of the Materials Advisory Board who have competence in the field.

In accordance with an agreement with the Office of the Director of Defense, Research and Engineering, this report is being distributed on the same date it is being transmitted to the Department of Defense. Therefore, as of this date, it has not been reviewed by the Office of the Director of Defense, Research and Engineering.

Very truly yours,



Carl S. Marvel, Chairman
Materials Advisory Board

Enclosure

MAB-196-M

Report of the
Subpanel on Quality Specifications
Refractory Metals Sheet Rolling Panel
Materials Advisory Board

RECOMMENDED QUALITY STANDARDS FOR TUNGSTEN SHEET
PRODUCED IN THE REFRACTORY METALS SHEET ROLLING PROGRAM

Division of Engineering and Industrial Research
National Academy of Sciences
National Research Council
Washington 25, D. C.

January 22, 1964

No portion of this report may be published without prior approval of the contracting agency.

This report prepared and submitted to the Office of the Director of Defense Research and Engineering under ARPA Contract Number SD-118, between the Department of Defense and the National Academy of Sciences.

CONTENTS

	<u>Page</u>
FOREWORD	v
1. SCOPE	1
2. PRODUCT LIMITATIONS	1
3. IDENTIFICATION	1
4. SAMPLING	2
5. TEST PROCEDURE	3
6. VISUAL INSPECTION	5
7. DIMENSIONAL TOLERANCES	5
8. SONIC INSPECTION	7
9. CHEMISTRY	7
10. TENSILE PROPERTIES	7
11. BEND TEST	11
12. METALLOGRAPHIC AND HARDNESS	11
13. REPORTS	11
ROSTER, QUALITY SPECIFICATIONS SUBPANEL	15
ROSTER, REFRACTORY METALS SHEET ROLLING PANEL	16

Tables

TABLE I - Sampling	2
TABLE II - Sheet Sampling	3
TABLE III - Thickness Tolerances	5
TABLE IV - Flatness Deviation Tolerances	6
TABLE V - Chemistry Allowables	7
TABLE VI - Tensile Property Tolerances	8
TABLE VII - Tensile Property Minimum Values	9
TABLE VIII - Maximum Permissible Bend Test Temperature	12

CONTENTS

	<u>Page</u>
<u>Figures</u>	
FIGURE 1 - Specimen Sampling	4
FIGURE 2 - Cross Section	10
FIGURE 3 - Sheet Test Report	13

FOREWORD

This revised sheet quality "specification" differs from MAB-184-M (Report of the Subpanel on Quality Specifications) in that it is limited to tungsten, and includes tensile property minimum values. These tensile minimums reflect realistic producer capabilities as demonstrated by the Navy contract NOW-60-0621-c with the Fansteel Metallurgical Corporation; and as such should be of particular interest to aerospace weapons designers.

These quality standards apply in general to sheet which is to be used in the as-furnished condition. Quality sampling specifications for plate, such as would be used in shear spinning, are covered in another publication (MAB-190-M). The plate produced under the Refractory Metal Sheet Rolling Program was insufficient to permit the establishment of minimum tensile or ductility values. Sheet destined for drastic working operations, such as cupping or drawing, might require a different microstructure (retaining a greater capacity for additional deformation) than that corresponding to the material in this report. For such other applications, the mechanical property levels would not correspond to those of the heavily cold worked sheet covered in these standards. Further experimental work would be required to define these property levels.

TUNGSTEN SHEET STANDARDS

SCOPE

1. This standard, written in the manner of a specification, describes tungsten sheet produced under contract from the Department of Defense in its Sheet Rolling Program.

PRODUCT LIMITATIONS

2. Any product between 0.187 and 0.005 inch inclusive in thickness, and 5 inches or more in width, is classified as sheet. All sheet shall be furnished in the stress-relieved condition.

IDENTIFICATION

3. a. All sheets shall be identified in the middle of each side of each sheet by this specification number, producer, sheet serial number, lot number, and nominal gage. A suitable marking fluid shall be used which can be removed with a cleaning solvent and which shall have no deleterious effect on the material.
- b. The sheet serial numbers shall run consecutively and be identified by the manufacturer in an accompanying report as to heat number and position of that sheet in the original ingot, e.g., top, middle, or bottom. In the case of powder metallurgy consolidation, billet rather than heat shall be identified.
- c. The lot is defined as follows for arc-melted or powder metallurgy consolidated material:

(1) Arc Melted Consolidation

All sheets of the same nominal thickness from the same heat with final rolling and both pre- and post-final rolling thermal treatments at the same time.

c. (Continued)

(2) Powder Metallurgy Consolidation

All sheets of the same nominal thickness with final rolling and both pre- and post-final rolling thermal treatments at the same time which have been made from billets pressed from a given blend of powders and sintered at the same time in a batch sintering operation, or during a given eight-hour shift in a continuous sintering operation, provided that the temperature and time of sintering are identical.

SAMPLING

4. a. All sheets produced by a contractor shall receive 100 per cent inspection visually, dimensionally, and sonically as described herein. In addition, one transverse bend test shall be made from one end of each sheet. The test temperature shall be as shown in Table VIII for the gage tested. The material for this test shall be excess from the end of the sheet and shall not diminish the size of the sheet ordered.
- b. With the exception of those tests described in paragraph 4. a., above, the number of sheets which shall be tested in any given lot are listed in Table I according to the size of the lot.

TABLE I - SAMPLING

Sheets Per Lot	Sheets Tested Per Lot
1	1
2 - 10	2
11 - 20	3
Over 20	4

- c. Table II indicates the number and size of test specimens which shall be taken from each sheet to be tested.
- d. Figure 1 shows the location of test specimens which shall be taken from each sheet to be tested.


TEST PROCEDURES

- 5. All tests will be performed in accordance with the "Evaluation Test Methods for Refractory Metal Sheet Material" by the Subpanel on Standardization of Test Methods, MAB Refractory Metals Sheet Rolling Panel. (Report MAB-192-M, dated April 22, 1963), or the latest revision thereof.

TABLE II
Sheet Sampling

Section No.	Test Name	Size of Specimen Blank, Inches	No. of Specimens Per Sheet	Fig. 1 Code No.
6.	Visual	Whole Sheet	Whole Sheet	-
7.	Dimensional	Whole Sheet	Whole Sheet	-
8.	Sonic	Whole Sheet	Whole Sheet	-
9.	Chemical	1.5 x 1.5	1	A
10.	Tensile			
10. a.	Longitudinal, 1000F	1.25 x 4	2	B
10. a.	Transverse, 1000F	1.25 x 4	2	C
10. b.	Longitudinal Notched, 1000F	1.25 x 4	2	D
10. c.	Tensile, Transverse 2000F	1.25 x 4	2	E
11.	Bend Test,			
	Transverse	1 x 4.25	2	F
	Longitudinal	1 x 4.25	1	G

FIGURE 1
Specimen Sampling

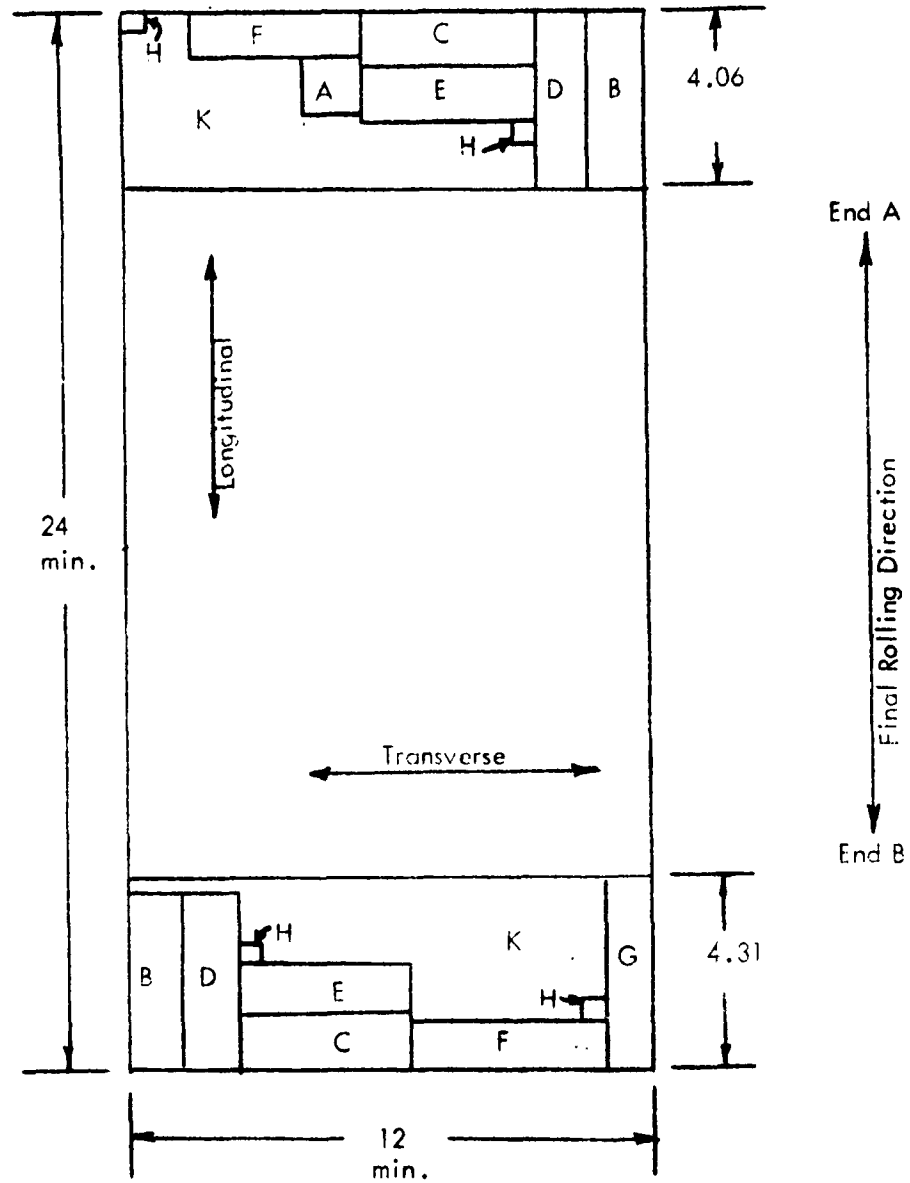

Dimensions allow for 1/16 inch saw cuts.

K Excess material for additional tests as required.

Note: Wider cuts may be taken, if dimensions permit.

Section No.	Test Name	Size of Specimen Blank, Inches	No. of Specimens Per Sheet	Fig. 1 Code No.
12.	Metallographic and Hardness Longitudinal or Transverse	0.5 x 0.5	4	H

VISUAL INSPECTION

6. All sheets on any one purchase order shall be furnished with the same finish treatment, e.g., pickled. Sheets which contain pits, cracks, scratches, non-metallic inclusions, or "fish scale" markings are unacceptable. Surface imperfections may be removed before shipment, but such removal shall not reduce the thickness of the material below that permitted by the tolerance for the thickness ordered. Such removal must be accomplished prior to final finish treatment, e.g., pickling.

DIMENSIONAL TOLERANCES

7. a. Tolerances on width shall be $\pm 1/16$ inch.
b. Tolerances on length shall be $\pm 3/16$ inch.
c. Tolerances on thickness shall be as shown in Table III below.
Measurements shall be taken one inch in from the edges on all sheets at the corners and mid sides to the nearest .0001 inch.

TABLE III
Thickness Tolerances $\pm$

Nominal Gage, Inches	Nominal Width, Inches		
	5 to 10	Over 10 to 18	Over 18
.005	.0007	.0007	.0010
Over .005 to .007	.0007	.00085	.0015
Over .007 to .016	.001	.0015	.002
Over .016 to .026	.0015	.0025	.003

TABLE III (Continued)

Nominal Gage, Inches	Nominal Width, Inches		
	5 to 10	Over 10 to 18	Over 18
Over .026 to .040	.002	.003	.004
Over .040 to .058	.003	.004	.005
Over .058 to .072	.004	.005	.006
Over .072 to .083	.004	.006	.007
Over .083 to .098	.004	.007	.0075
Over .098 to .114	.005	.007	.008
Over .114 to .130	.005	.008	.010
Over .130 to .145	.006	.008	.010
Over .145 to .187	.007	.009	.010

d. Edge camber shall be 3/16 inch maximum in 8 feet.

e. Flatness deviation tolerances shall be as shown in Table IV.

Flatness deviation shall be determined by the method shown in Figure 2. The actual values shall be reported. In determining flatness the sheet shall not be subject to external pressure at any point, but shall be allowed to lie freely on a flat surface during measurement.

TABLE IV
Flatness Deviation Tolerances

Nominal Gage, Inches	Tolerance, %
.005	6
Over .005 to .015 inclusive	6
Over .015 to .025 inclusive	5
Over .025 to .040 inclusive	5
Over .040 to .060 inclusive	5
Over .060 to .100 inclusive	4
Over .100	4

SONIC INSPECTION

8. Determination of the presence of definite laminations in the sheets will be accomplished with sonic inspection techniques. A grid pattern no more than two inches on a side will be used for the survey. Laminated areas will be marked on the sheet. Sheets showing such areas will be subject to rejection at the discretion of the contracting agency.

CHEMISTRY

9. Chemical determinations shall be made on individual sheets representative of each lot in accordance with Tables I and II. Sampling shall be made in accordance with Figure 1. Analysis will be made for the principal impurity elements and the three interstitial elements: oxygen, nitrogen, and carbon. Maximum permissible impurity levels are as shown in Table V.

TABLE V
Chemistry Allowables, ppm Maximum

<u>Element</u>	<u>ppm, Max.</u>	<u>Element</u>	<u>ppm, Max.</u>
C	50	Sn	20
O	50	Ca	20
N	20	Co	10
H	10	Pb	10
Mo	100	Mg	10
Fe	50	Mn	10
Si	40	Ag	10
Al	40	V	10
Zr	50	Ti	10
Cr	20		
Ni	20		
Cu	20		

Tungsten 99.95% minimum, by difference

TENSILE PROPERTIES

10. a. Transverse and longitudinal 1000°F tensile specimens shall be taken from each end of each sheet selected in accordance with

a. (continued)

Table I and cut as shown in Figure 1. The allowable variation for all specimens in any one lot shall not be greater than that shown in Table VI. The minimum value for any test shall not be less than that shown in Table VII.

b. Longitudinal notched 1000°F tensile specimens shall be taken from each end of each sheet selected in accordance with Table I and cut as shown in Figure 1. The notched-unnotched tensile ratio shall not be less than one.

c. Transverse 2000°F tensile specimens shall be taken from each end of each sheet selected in accordance with Table I and cut as shown in Figure 1. The allowable variation for all specimens in any one lot shall not be greater than that shown in Table VI. The minimum value for any test shall not be less than that shown in Table VII.


TABLE VI
Tensile Property Tolerances

Property	Variation from Average for Lot
Ultimate Tensile Strength, 1000°F	
Longitudinal	$\pm 15\%$
Transverse	$\pm 12\%$
Tensile Yield Strength, 1000°F	
Longitudinal	$\pm 20\%$
Transverse	$\pm 12\%$
Ultimate Tensile Strength, 2000°F	
Transverse	$\pm 20\%$
Tensile Yield Strength, 2000°F	
Transverse	$\pm 20\%$

TABLE VII
Tensile Property Minimum Values

Test	Temperature °F	Direction*	Nominal Gage, inches				
			.010-.019	.020-.039	.040-.079	.080-.124	.125-.187
Ultimate Tensile Strength, ksi	1000	T	130	120	85	75	75
	1000	L	120	110	75	75	75
	2000	T	75	75	60	60	60
Tensile Yield Strength - ksi	1000	T	100	100	70	60	60
	1000	L	90	90	60	60	60
	2000	T	60	60	50	50	50
Elongation, % in 1 in.	1000	T	4	5	6	6	6
	1000	L	4	5	6	6	6
	2000	T	6	6	6	6	6

* L = Longitudinal
T = Transverse

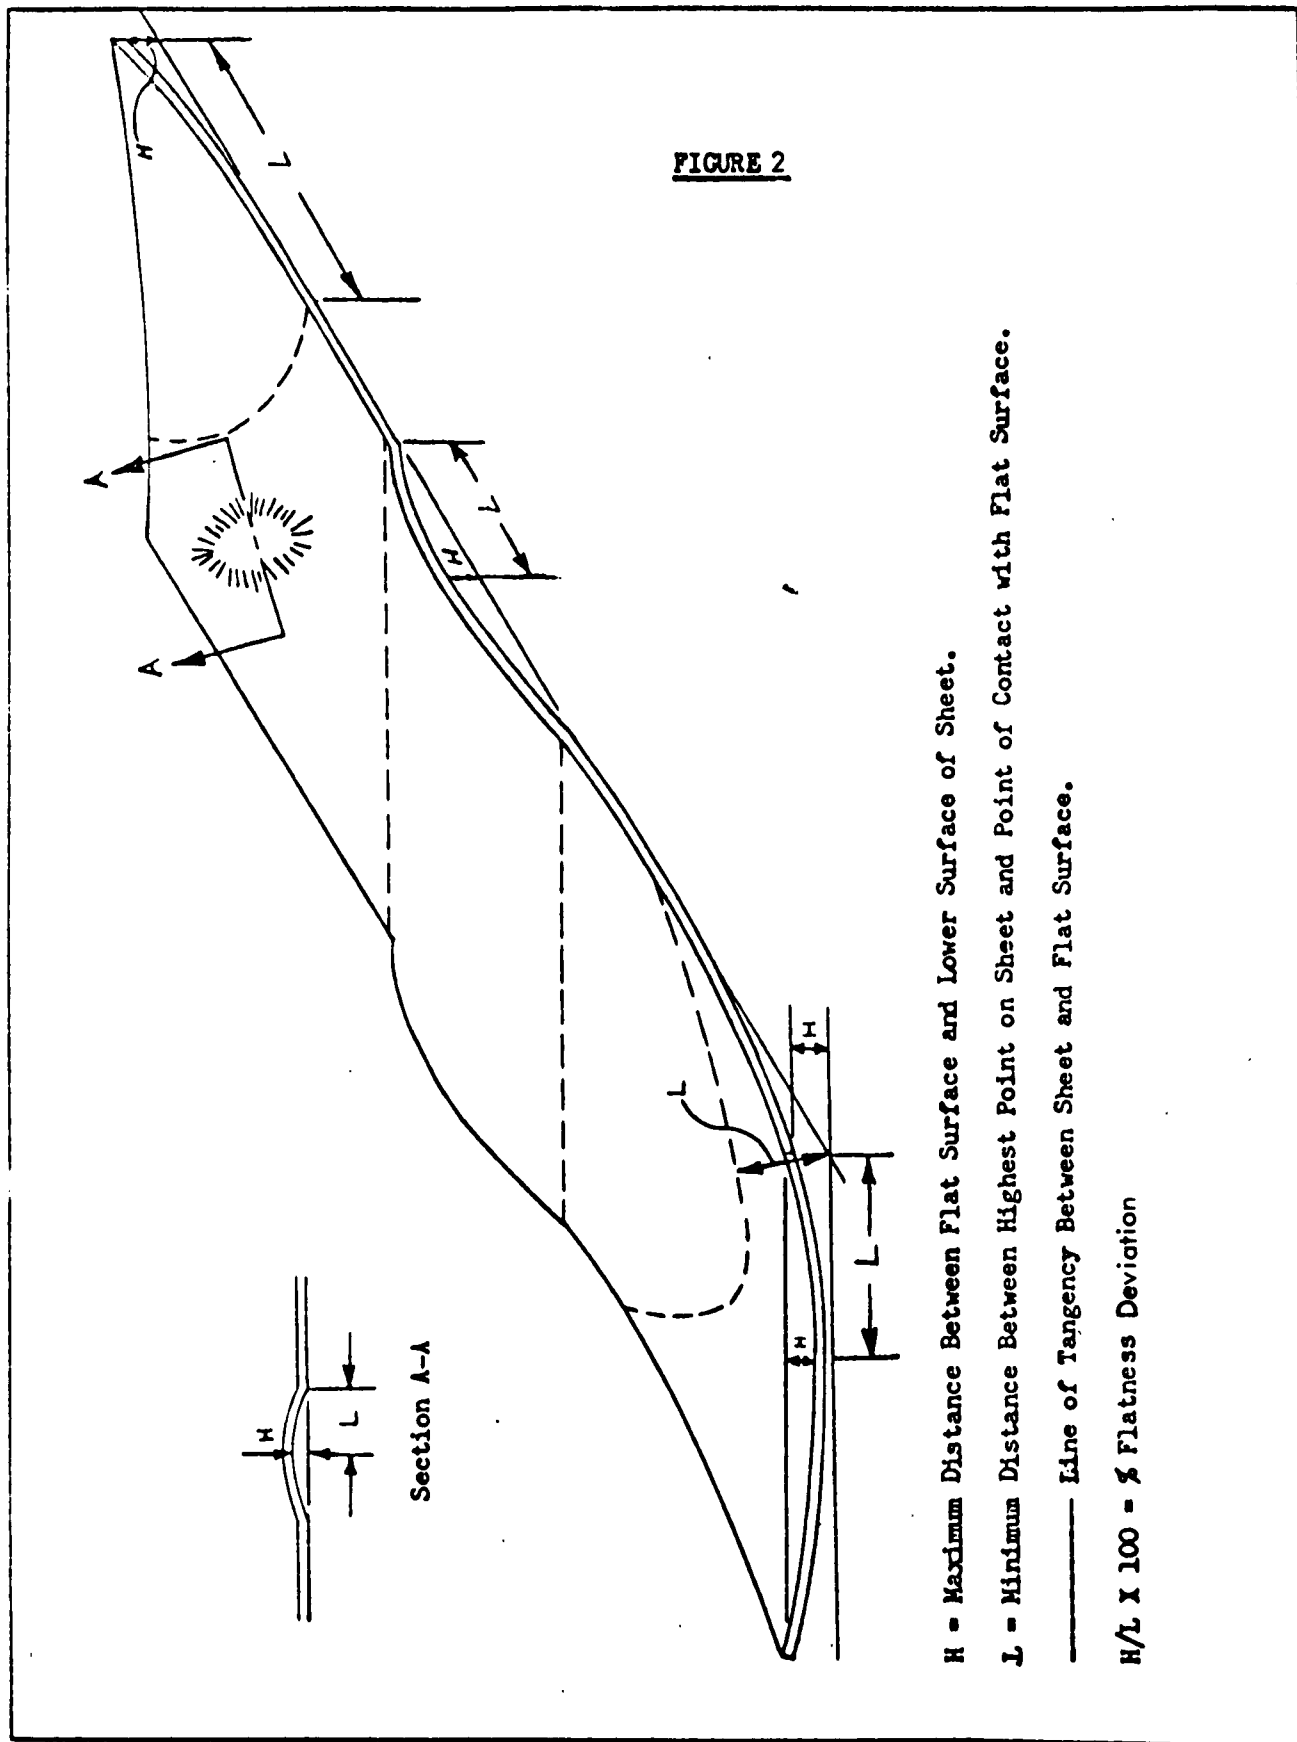

BEND TEST

11. a. Transverse and longitudinal bend specimens shall be taken from each end and from one end, respectively, from each sheet selected in accordance with Table I and cut as shown in Figure 1. Tests shall be made using a 4T (T = thickness) bend radius at the temperature indicated in Table VIII for the gage tested. If any of the specimens fail to bend to 90° at temperature, the lot shall be subject to rejection.
- b. In addition to the above, one transverse bend specimen shall be taken from one end of each sheet (see paragraph 4.a.) in the lot and tested as described above. Failure to pass the above test subjects that particular sheet to rejection independently of results obtained from lot sampling tests.

METALLOGRAPHIC AND HARDNESS

12. a. Metallographic specimens shall be taken in accordance with Table I and Figure 1 for information only to determine structure (average grain diameter, if recrystallized) and the occurrence of solid non-metallic inclusions or intermetallic compounds. Photomicrographs shall be taken on all specimens at 250X and at 1000X.
- b. Diamond pyramid hardness readings shall be taken on all metallographic specimens in the middle of the section. The load shall be recorded.

REPORTS

13. It is recommended that the format of the reports follow the example given in Figure 3 and be furnished to the contracting officer.

TABLE VIII
Maximum Permissible Bend Test Temperature
(Bend Radius = 3X thickness)

<u>Nominal Gage, Inches</u>	<u>Test Specimen Direction*</u>	<u>Maximum Temperature, °F</u>
.005 to .020 inclusive	L	300
.005 to .020 inclusive	T	400
Over .020 to .040 inclusive	L	400
Over .020 to .040 inclusive	T	500
Over .040 to .100 inclusive	L	500
Over .040 to .100 inclusive	T	600
Over .100 to .187 inclusive	L	600
Over .100 to .187 inclusive	T	700

* L = longitudinal, T = transverse

FIGURE 3
Sheet Test Report

Alloy: _____
Producer: _____
P. O. Number: _____
Condition: _____
Month and Year Produced: _____

Sheet Serial No.: _____
Lot No.: _____
*Heat No.: _____
**Position in Ingot: _____
Sheet Size (Nom.)
Gage: _____
Length: _____
Width: _____

Visual Inspection:

Dimensional:

Length: _____

Width: _____

Camber: _____

Thickness: 1 _____ 2 _____ 3 _____
4 _____ 5 _____ 6 _____
7 _____ 8 _____

1	4	6
2		7
3	5	8

Flatness Deviation: _____

Oil Can: _____

Sonic: _____

Chemistry of Sheet:

Impurity: 1 _____ 2 _____ 3 _____ 4 _____
5 _____ 6 _____ 7 _____ 8 _____

Interstitial: 0 _____ N _____ C _____

* In the case of powder metallurgy consolidation - "Billet No."

** In the case of powder metallurgy consolidation - "Density of Billet: _____%"

Tensile Properties	Ultimate, psi	Yield, psi	Elong., % in _____
1000°F			
End A, Transverse	_____	_____	_____
End A, Longitudinal	_____	_____	_____
End B, Transverse	_____	_____	_____
End B, Longitudinal	_____	_____	_____
2000°F			
End A, Transverse	_____	_____	_____
End B, Transverse	_____	_____	_____
1000°F			
Notched			
End A, Longitudinal	_____	_____	_____
End B, Longitudinal	_____	_____	_____
Bend Test: (°F, see Table VIII)	Bend, Degrees	Springback, Degrees	°F
End A, Transverse	_____	_____	_____
End B, Transverse	_____	_____	_____
End B, Longitudinal	_____	_____	_____
Metallographic Results:			
Structure: _____			
Average Grain Diameter: _____			
Inclusions: _____			
Hardness Results:			
Readings, DPH	_____	_____	_____
Average, DPH	_____		
Load, grams	_____		

MATERIALS ADVISORY BOARD
SUBPANEL ON QUALITY SPECIFICATIONS
of the
REFRACTORY METALS SHEET ROLLING PANEL

Chairman: Mr. John T. Stacy
Senior Group Engineer
Boeing Airplane Company
Aero-Space Division
P.O. Box 3707
Seattle 24, Washington

Members

Mr. S. E. Bramer, Head
Product & Process Development
Structural Materials Division
Aerojet General Corporation
Azusa, California

Mr. Robert R. Freeman
Marketing Manager
Refractory Metal Division
Climax Molybdenum Co. of Michigan (Inc.)
14410 Woodrow Wilson
Detroit 38, Michigan

Mr. Basil T. Lanphier
Chief Metallurgist
Carpenter Steel Company
Reading, Pennsylvania

Staff Metallurgist - Dr. Joseph R. Lane

MATERIALS ADVISORY BOARD

REFRACTORY METALS SHEET ROLLING PANEL

Chairman: Mr. G. Mervin Ault, Assistant Chief
Materials & Structure Division
Lewis Research Center
National Aeronautics & Space Administration
21000 Brookpark Road
Cleveland 35, Ohio

MAB Staff Metallurgist: Dr. Joseph R. Lane

Members

Dr. Robert I. Jaffee
Associate Manager
Department of Metallurgy
Battelle Memorial Institute
505 King Avenue
Columbus 1, Ohio

Dr. William Rostoker
Assistant Manager
Metals Research Department
Armour Research Foundation
Technology Center
Chicago 16, Illinois

Mr. Alan V. Levy
Division Manager
Materials & Fabrication
Solid Rocket Plant
Aerojet General Corporation
Sacramento, California

Dr. L. L. Seigle
Manager, Metallurgical Laboratory
General Telephone & Electronics
Laboratories, Inc.
P. O. Box 59
Bayside, New York

Mr. Roger A. Perkins
Metallurgy and Ceramics Research
Lockheed Aircraft Corporation
Missile and Space Division
3251 Hanover Street
Palo Alto, California

Mr. John T. Stacy
Senior Group Engineer
Boeing Airplane Company
Aero-Space Division
P. O. Box 3707
Seattle 24, Washington

Mr. L. M. Raring, Chief
Metallurgical & Chemical Labs.
Pratt & Whitney Aircraft
CANEL, Box 611
Middletown, Connecticut

Liaison Representatives

DOD	Mr. John C. Barrett, Office of the Director of Defense Research & Engineering, The Pentagon, Washington 25, D. C.
RTD	Mr. T. D. Cooper, Technical Manager for High Temperature Metals, Physical Metallurgy Branch, Materials & Ceramics Div. Code MAMP, AF Materials Lab, Wright-Patterson AFB, Ohio
	Mr. George Glenn, Code MATB, Wright-Patterson AFB, Ohio
	Mr. I. Perlmutter, MAMP, Chief, Physical Metallurgy Branch Metals & Ceramics Div., AF Materials Laboratory, Wright-Patterson AFB, Ohio
Army	Mr. S. V. Arnold, Army Materials Research Agency, Watertown Arsenal, Watertown 72, Massachusetts
BuWeps	Mr. I. Machlin, Materials Division, RRMA-23, Bureau of Naval Weapons, Department of the Navy, Washington 25, D. C.
	Mr. N. E. Promisel, Chief Materials Engineer, RRMA, Bureau of Naval Weapons, Department of the Navy, Washington, D. C.
AEC	Mr. S. S. Christopher, Reactor Development Division, Atomic Energy Commission, Washington 25, D. C.

NATIONAL ACADEMY OF SCIENCES— NATIONAL RESEARCH COUNCIL

The National Academy of Sciences—National Research Council is a private, nonprofit organization of scientists, dedicated to the furtherance of science and to its use for the general welfare.

The Academy itself was established in 1863 under a Congressional charter signed by President Lincoln. Empowered to provide for all activities appropriate to academies of science, it was also required by its charter to act as an adviser to the Federal Government in scientific matters. This provision accounts for the close ties that have always existed between the Academy and the Government, although the Academy is not a governmental agency.

The National Research Council was established by the Academy in 1916, at the request of President Wilson, to enable scientists generally to associate their efforts with those of the limited membership of the Academy in service to the nation, to society, and to science at home and abroad. Members of the National Research Council receive their appointments from the President of the Academy. They include representatives nominated by the major scientific and technical societies, representatives of the Federal Government, and a number of members-at-large. In addition, several thousand scientists and engineers take part in the activities of the Research Council through membership on its various boards and committees.

Receiving funds from both public and private sources, by contributions, grant, or contract, the Academy and its Research Council thus work to stimulate research and its applications, to survey the broad possibilities of science, to promote effective utilization of the scientific and technical resources of the country, to serve the Government, and to further the general interests of science.

MATERIALS ADVISORY BOARD

The Materials Advisory Board is a part of the Division of Engineering and Industrial Research of the Academy-Research Council. It was organized in 1951 under the name of the Metallurgical Advisory Board, with assignments from the then existing Research and Development Board of the Department of Defense. At that time, the Research and Development Board requested the Board to accept tasks covering a broad spectrum of metallurgical science and technology as related to the Armed Services, and to include certain other areas such as collection and dissemination of information, and cooperation with professional societies in publication of significant metallurgical data.

Since the organization date, the above scope has been expanded to include organic and inorganic nonmetallic materials, and the name has been changed to the Materials Advisory Board. Concurrently, the Board's membership, staff, and operations have been adjusted to encompass the greater diversity of materials and to concentrate on materials research and development, excluding other activities except to the extent that they support and strengthen the Board's fulfillment of its primary responsibility.

The Office of the Director of Defense Research and Engineering, Office of the Secretary of Defense, is the government agency which now requests specific consulting and advisory services under this broadened program. Under a contract between the Office of the Secretary of Defense and the National Academy of Sciences, the Board's assignment is:

"... at the written request of the Director of Defense Research and Engineering, or his designated representative, to conduct studies, surveys, make critical analyses, and prepare and furnish to the Director of Defense Research and Engineering advisory and technical reports, with respect to the entire field of materials research, including the planning phases thereof; and shall, in addition, perform such other services as may be agreed upon in writing, from time to time, by the Director of Defense Research and Engineering and the President of the Contractor.

"Task assignments under this contract will be as mutually agreed by the Director of Defense Research and Engineering or his designated representative and the Contractor. Recommendations for tasks may be proposed to the Director of Defense Research and Engineering by agencies of the Military Departments, the Office of the Secretary of Defense, or the Contractor."