

UNCLASSIFIED

AD 4 3 7 8 8 1

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

64-12

FTDM-3177
15 April 1964

437881

CATALOGED BY DDC


AS AD NO.

437881

MATERIAL EVALUATION OF H-11 HIGH
STRENGTH STEEL FOR F-111

Published and distributed under Contract No.
AF33(657)-11214, Air Force Materials Laboratory,
Aeronautical Systems Division, Air Force Systems
Command, Wright-Patterson Air Force Base, Ohio.

GENERAL DYNAMICS | FORT WORTH

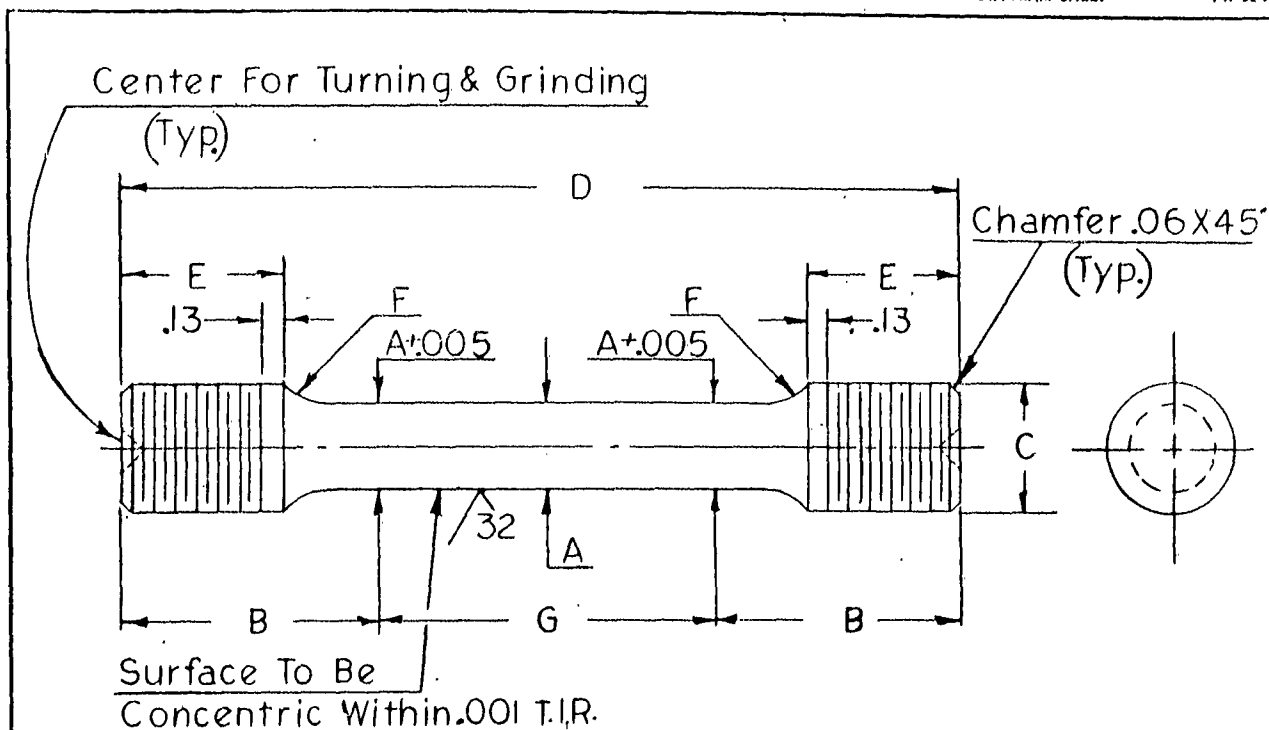


1. Unless otherwise specified tolerances are as follows:
 Linear dimensions - .xx $\pm$.03 .xxx $\pm$.010
 Angular $\neq$ 0° - 30°
2. Material to be as specified.
3. Grain direction to be longitudinal unless otherwise specified.

Figure 1.

Dash No	A	B	C	D	E	F (Min)	G (Gage Length)
- 1	.505 ± .010	1.50	3/4 - 10 NC	5.00	1.00	.38	2.000 ± .005
- 2	.357 ± .007	1.30	5/8 - 11 NC	4.00	.88	.25	1.400 ± .005
- 3	.252 ± .005	1.06	1/2 - 13 NC	3.12	.75	.19	1.000 ± .005
- 4	.200 ± .004	.85	5/16 - 24 NF	2.50	.63	.13	.800 ± .005
DRAWN	R. Cathey		TENSILE TEST				FTJ-10940
CHECKED	A. J. J. J.		SPECIMEN-ROUND				Full Scale
ENG.							
PROJECT			CONSOLIDATED VULTEE AIRCRAFT CORPORATION FORT WORTH DIVISION - FORT WORTH, TEXAS				

ISSUED:

REVISED:

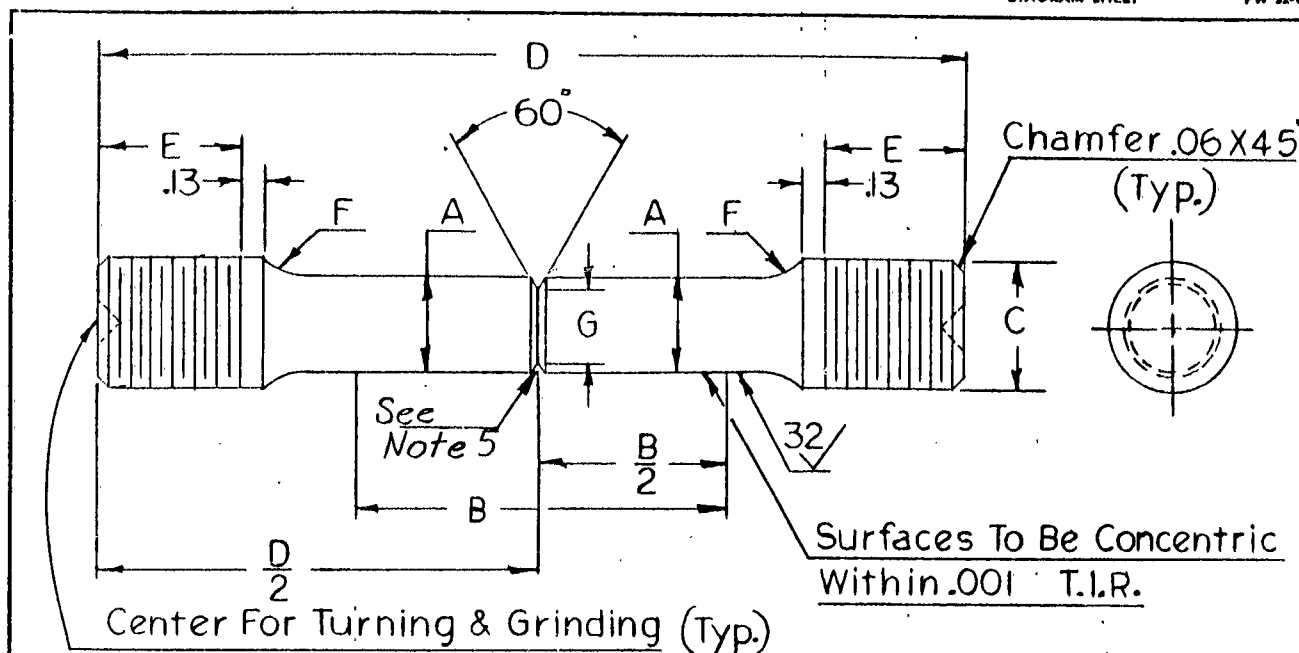

NOTES:

1. Unless otherwise specified tolerances are as follows:
 Linear dimensions - .xx $\pm$.03 .xxx $\pm$.010
 Angular dimensions - $\pm$ 0° - 30°
2. Material to be as specified.
3. Grain direction to be longitudinal unless otherwise specified.
4. Fabricate in accordance with the following procedure:
 - 4.1 Center ends & remove all burrs - center holes must be concentric
 - 4.2 Rough machine to 0.020 in. oversize omitting the notch.
 - 4.3 Heat treat as required.
 - 4.4 Machine or grind to finished dimensions except notch.
 - 4.5 Machine notch to .020 in. oversize using a carbide tool & lard oil coolant.
 - 4.6 Sharpen carbide tool to required size and finish machine notch.
 - 4.7 Examine notch under a microscope for surface smoothness and correct contour.

Dash No.	Notch Dia. (G)	Notch Radius	K ₂ (max)	K ₁ (min)
-5	.505	.005 $\pm$.001	6.9	5.7
-6	.357	.003 $\pm$.0015	8.0	5.5
-7	.252	.002 $\pm$.0005	8.0	5.7

Figure 2.

Dash No	A	B	C	D	E	F	G
-5	.712	2.25	3/4 10 NC	5.00	1.00	.38	.505 $\pm$.010
-6	.505	2.25	5/8 11 NC	4.50	.88	.25	.357 $\pm$.007
-7	.357	1.25	1/2 13 NC	3.13	.75	.19	.252 $\pm$.005

DRAWN	R. Carley	DATE		TENSILE SPECIMEN - NOTCHED	FTJ-10940
CHECKED					Scale - Full
ENG.					
PROJECT					

CONSOLIDATED VULTEE AIRCRAFT CORPORATION
FORT WORTH DIVISION - FORT WORTH, TEXAS

ISSUED:

REVISED:




GENERAL DYNAMICS | FORT WORTH

PAGE 4
REPORT NO. FTDM 3177
MODEL F-111
DATE 5 February 1964


Grinding Notes

1. Remove Equal Amounts From Both Sides.
2. Use Soft Wheel.
3. Use Maximum Coolant.
4. Do Not Burn.
5. Grind Longitudinally.
6. Bake After Grinding - 300°F. One Hour.

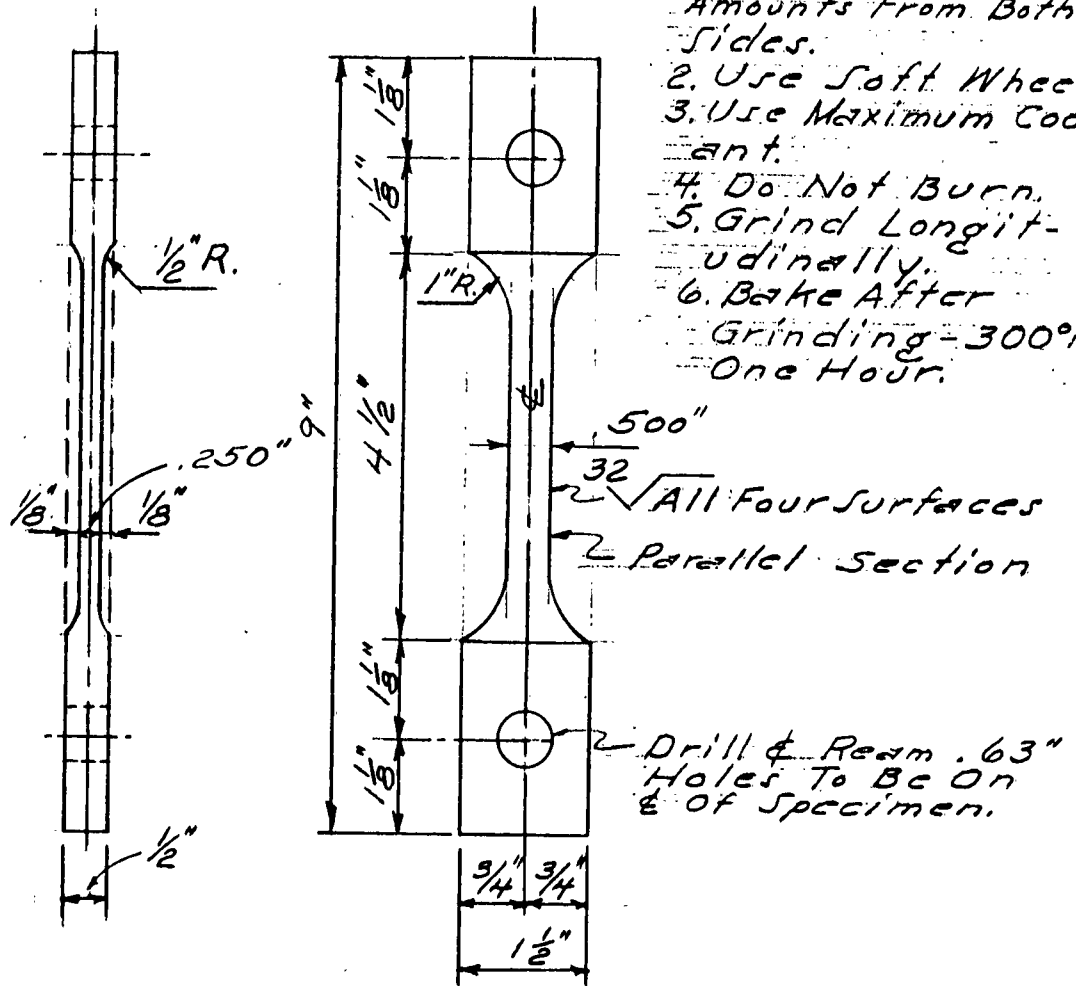



Transverse Weld Tensile Specimen
From 1/2\" Plate

Figure 3

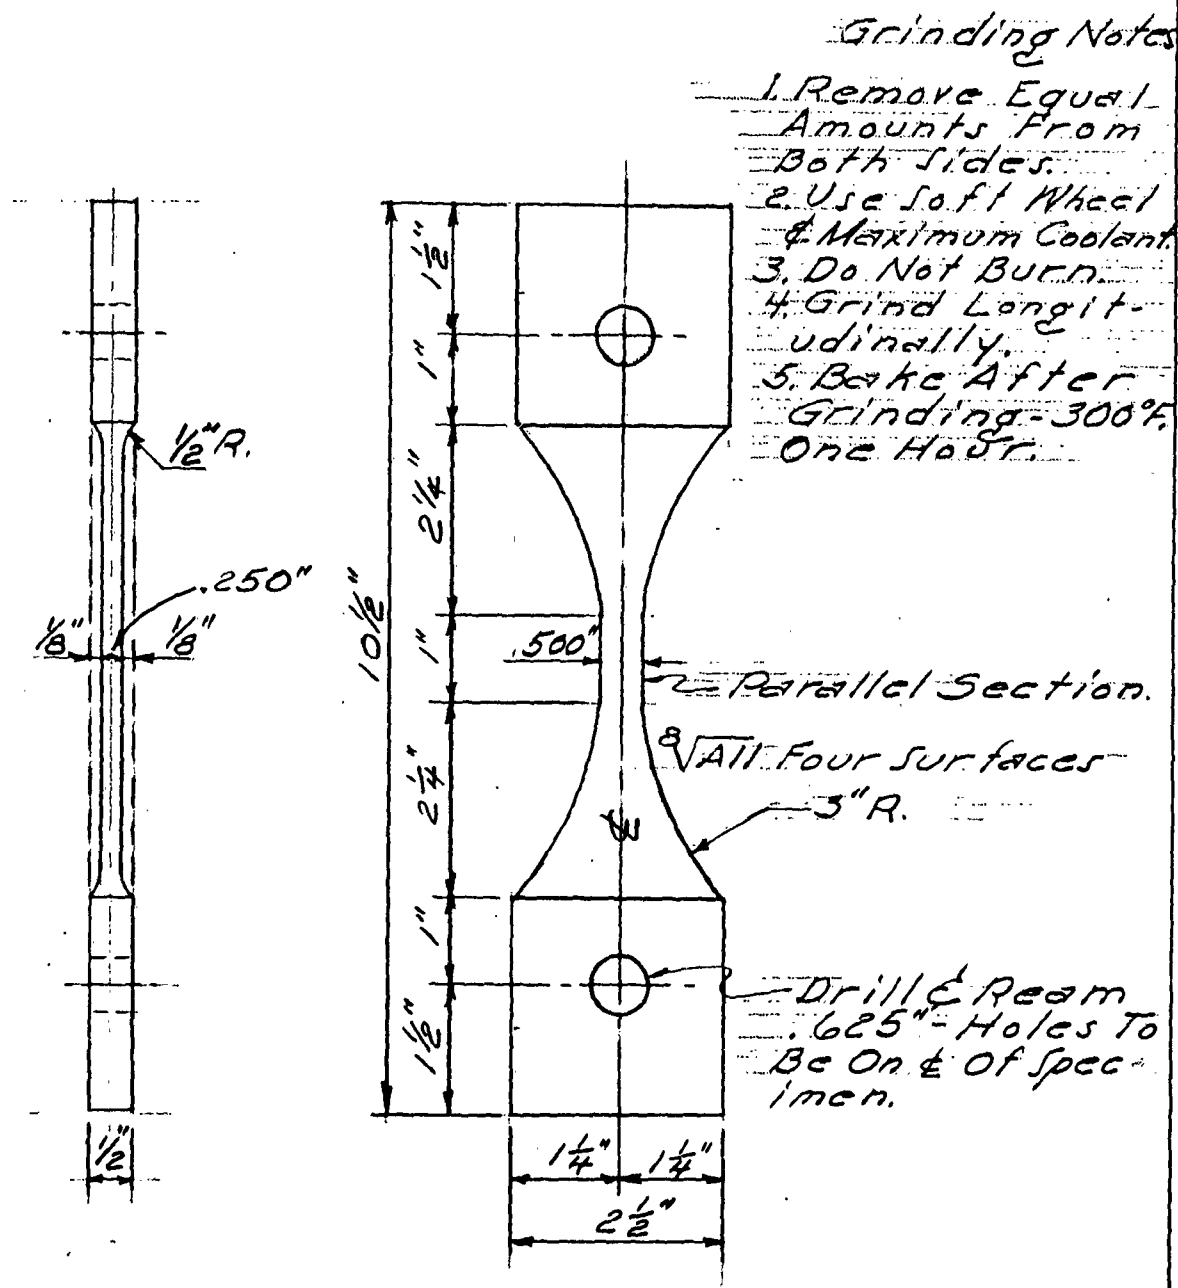


Transverse Weld Fatigue Specimen
From 1/2" Plate

Figure 4.

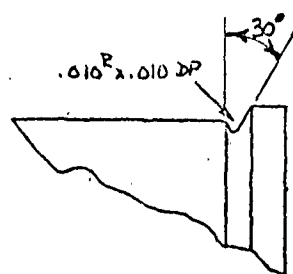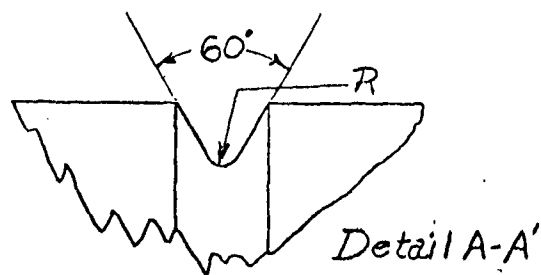

DASH NO	K_t	C $\pm .005$	D $\pm .005$	R $\pm .001$
-91	2	.430	.300	.049
-92	3	.430	.300	.016
-93	4	.430	.300	.008
-94	2	.357	.252	.037
-95	3	.357	.252	.013
-96	5	.357	.252	.004

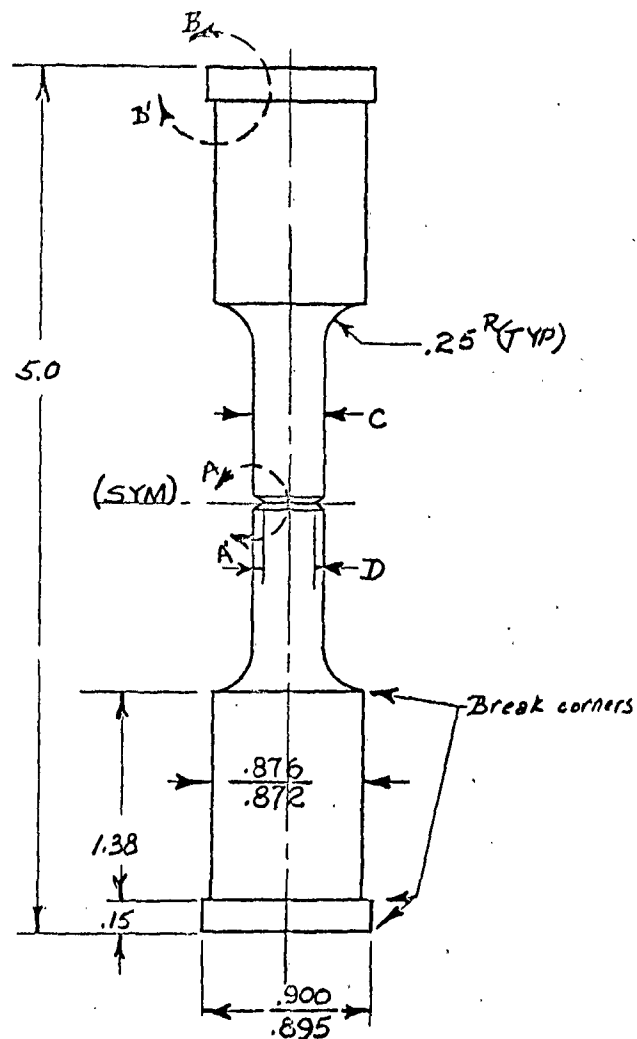



NOTES:


- 1) Turn on centers.
- 2) Allow .020 on dias, for heat treat.
- 3) Not run after heat treat
- 4) Polish notch in lathe.


Figure 5.


MAT'L		H'TREAT		Fatigue Test Specimen, $K_t > 1$ Collect Grip	TOOL NO. FTJ1094
TOL.	0.0 $\pm .10$	0.00 $\pm .030$	0.000 $\pm .010$		ANG. $\pm$
DRAWN R. G. Schilz		APPROVED		CONVAIR A DIVISION OF GENERAL DYNAMICS CORPORATION (FORT WORTH)	DEPT. 24 FW-32-0-24
CHECKED		DATE 31 Oct '63			

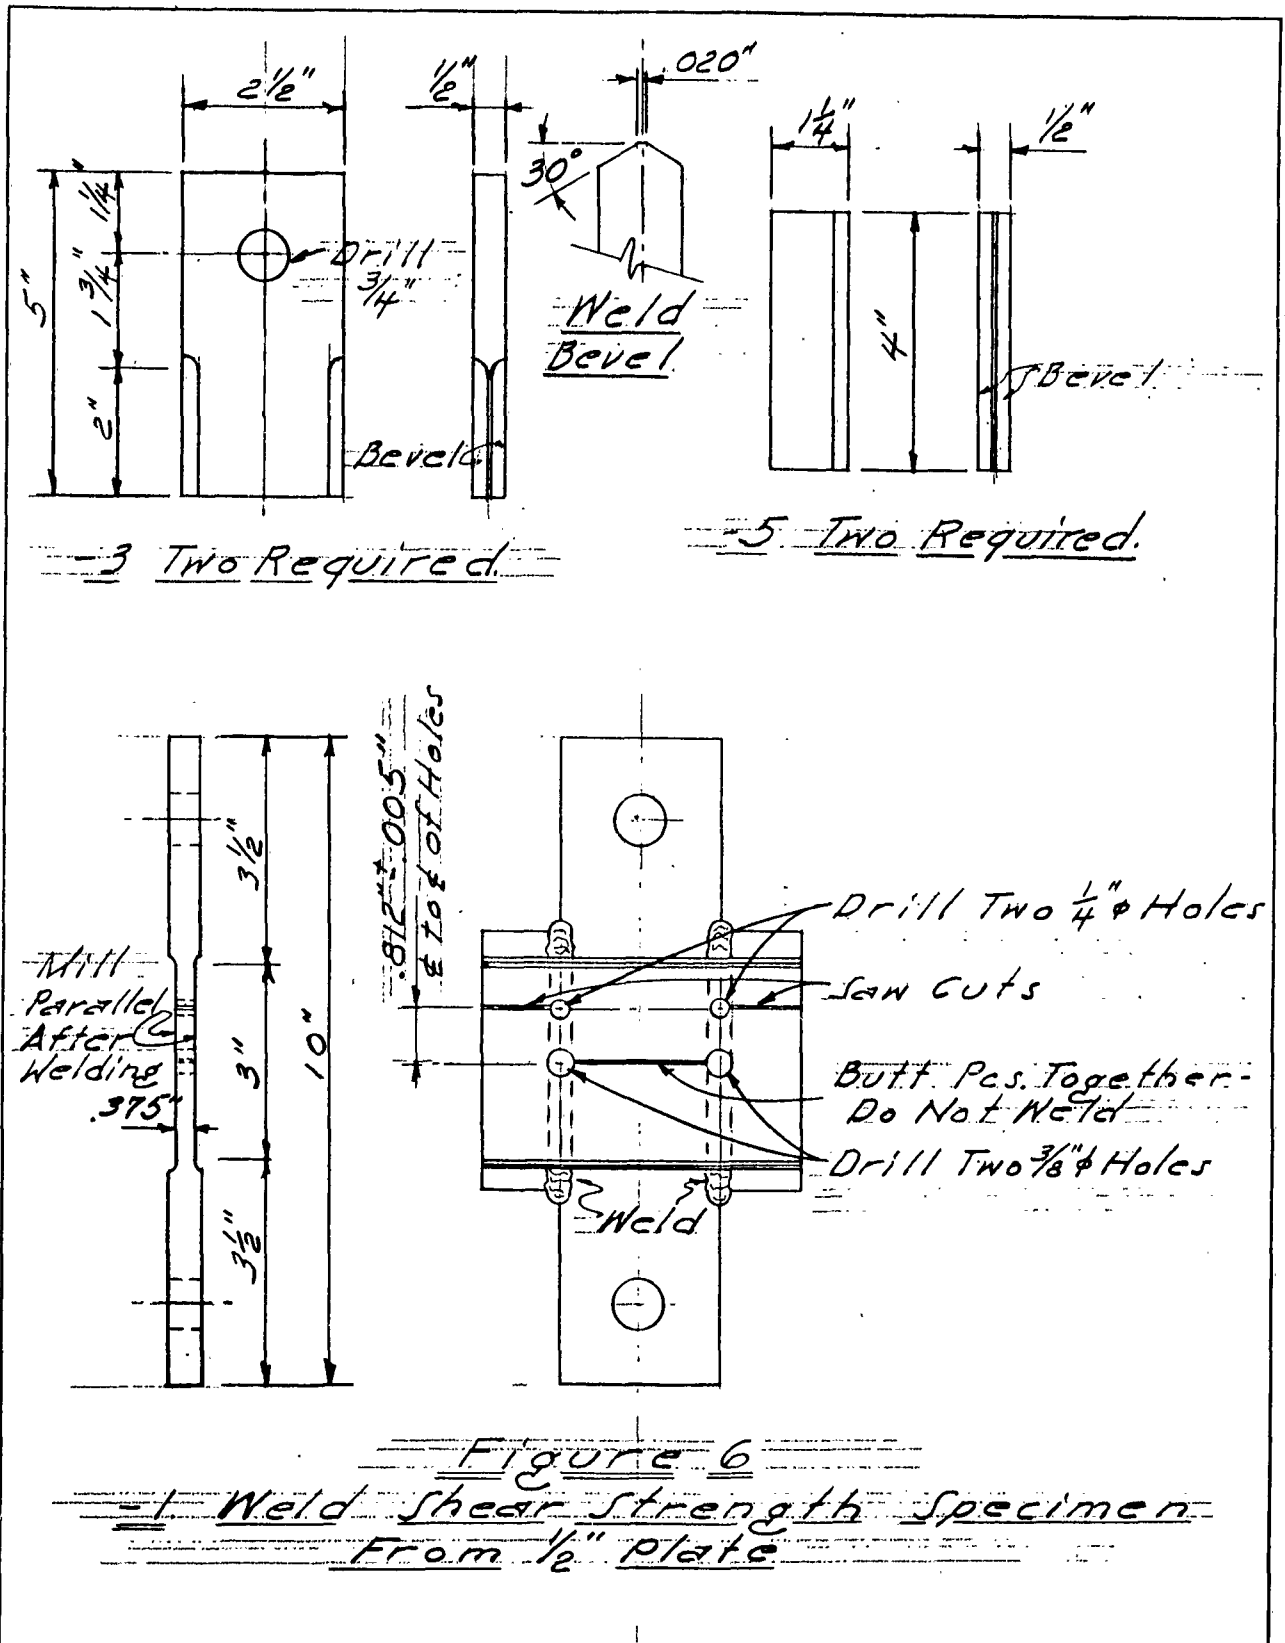


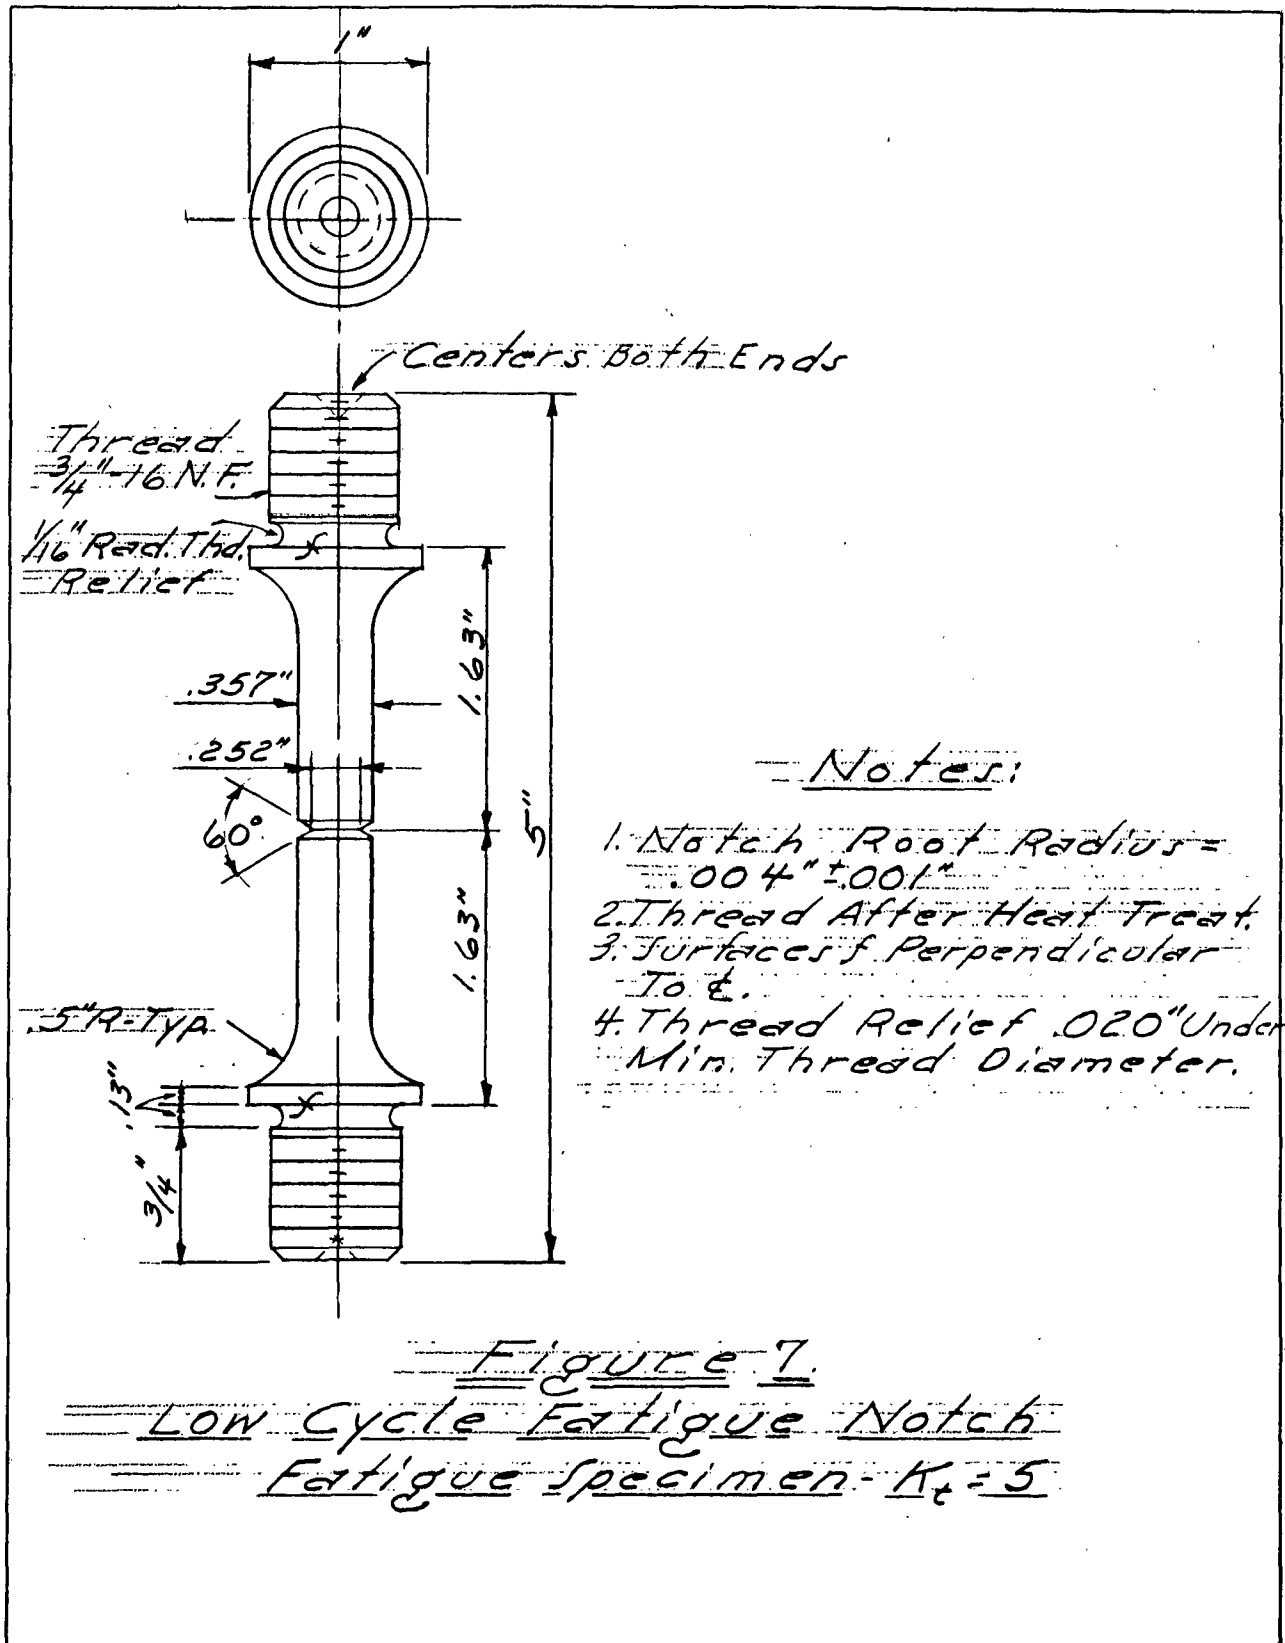

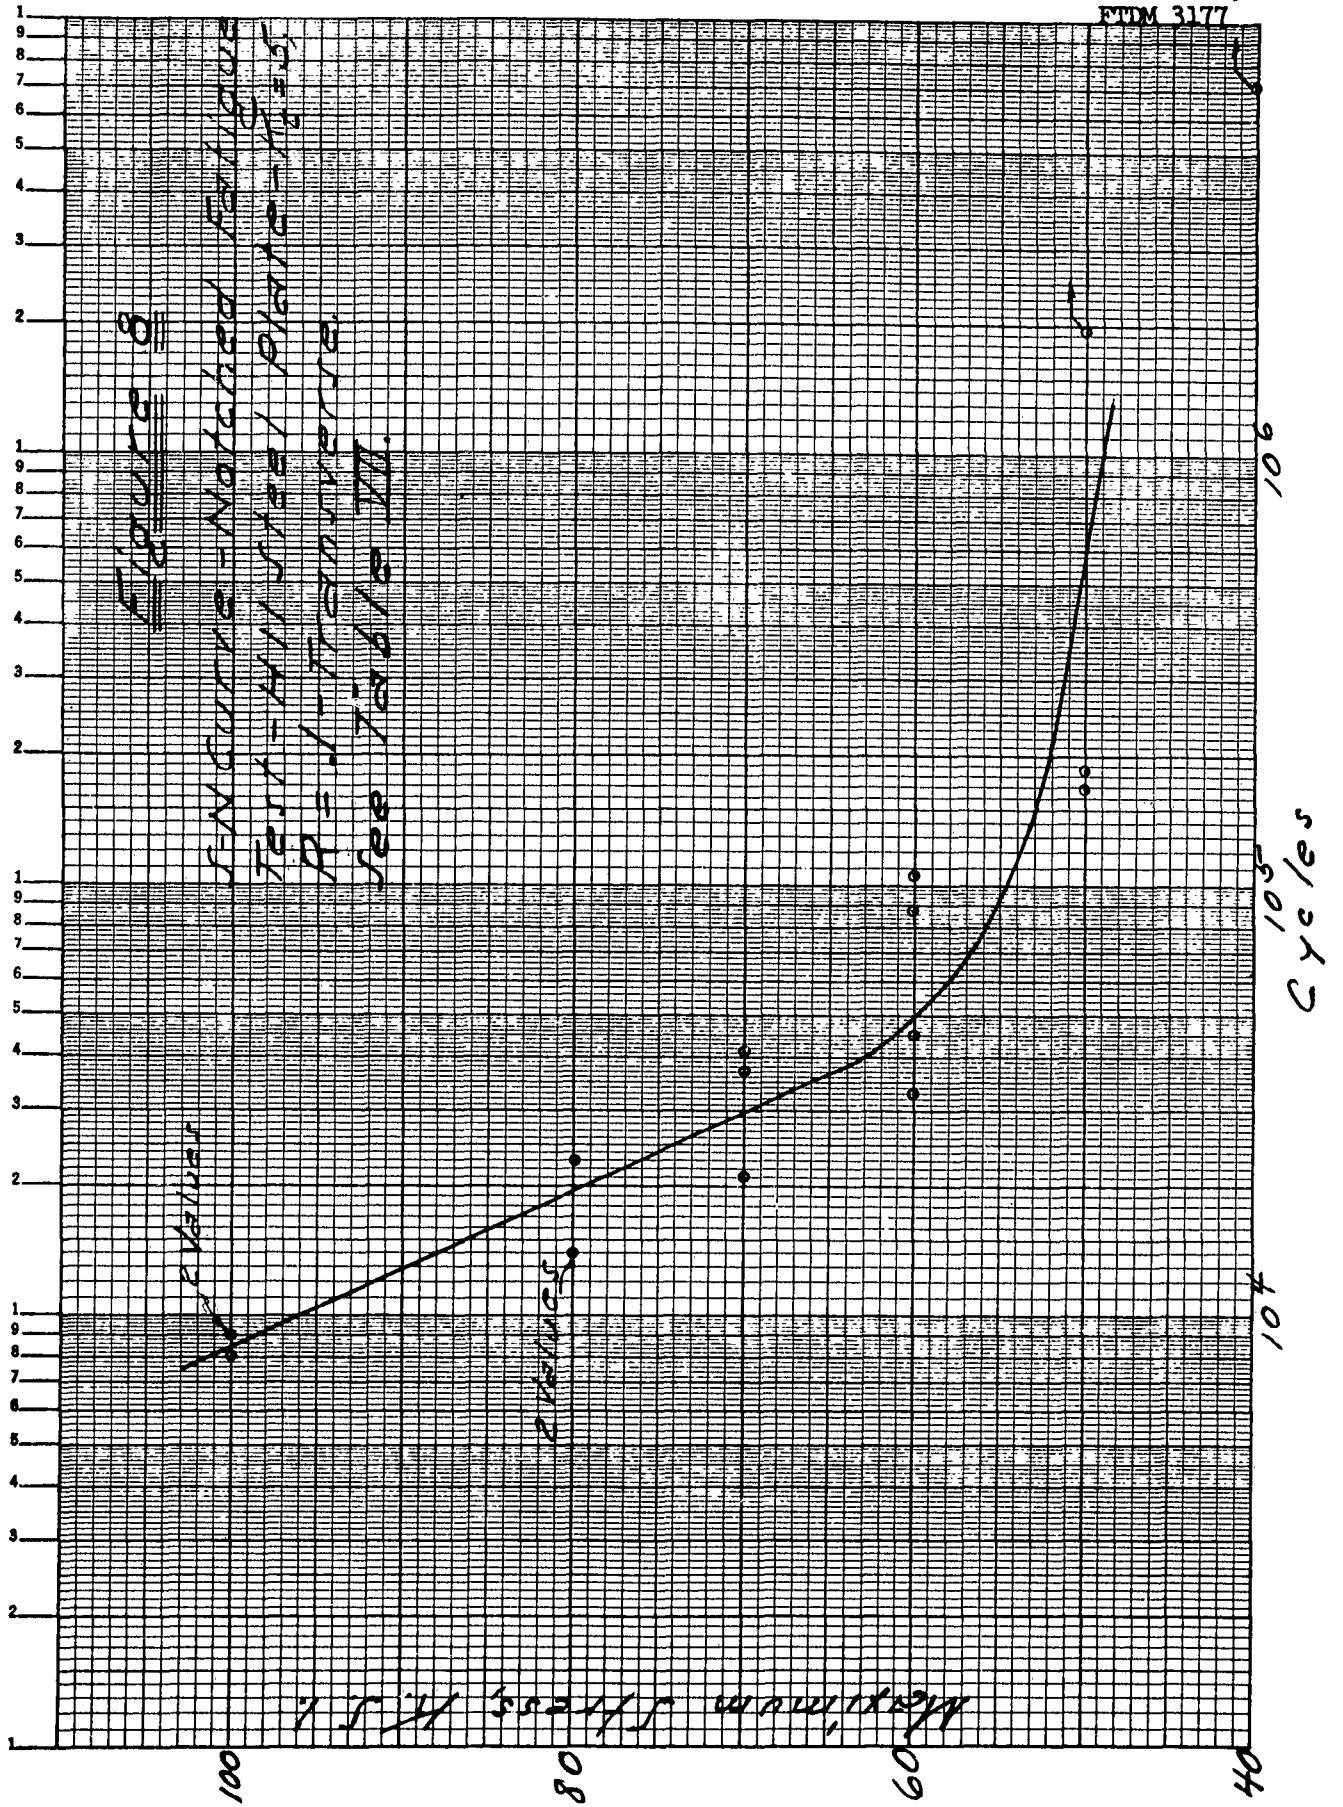

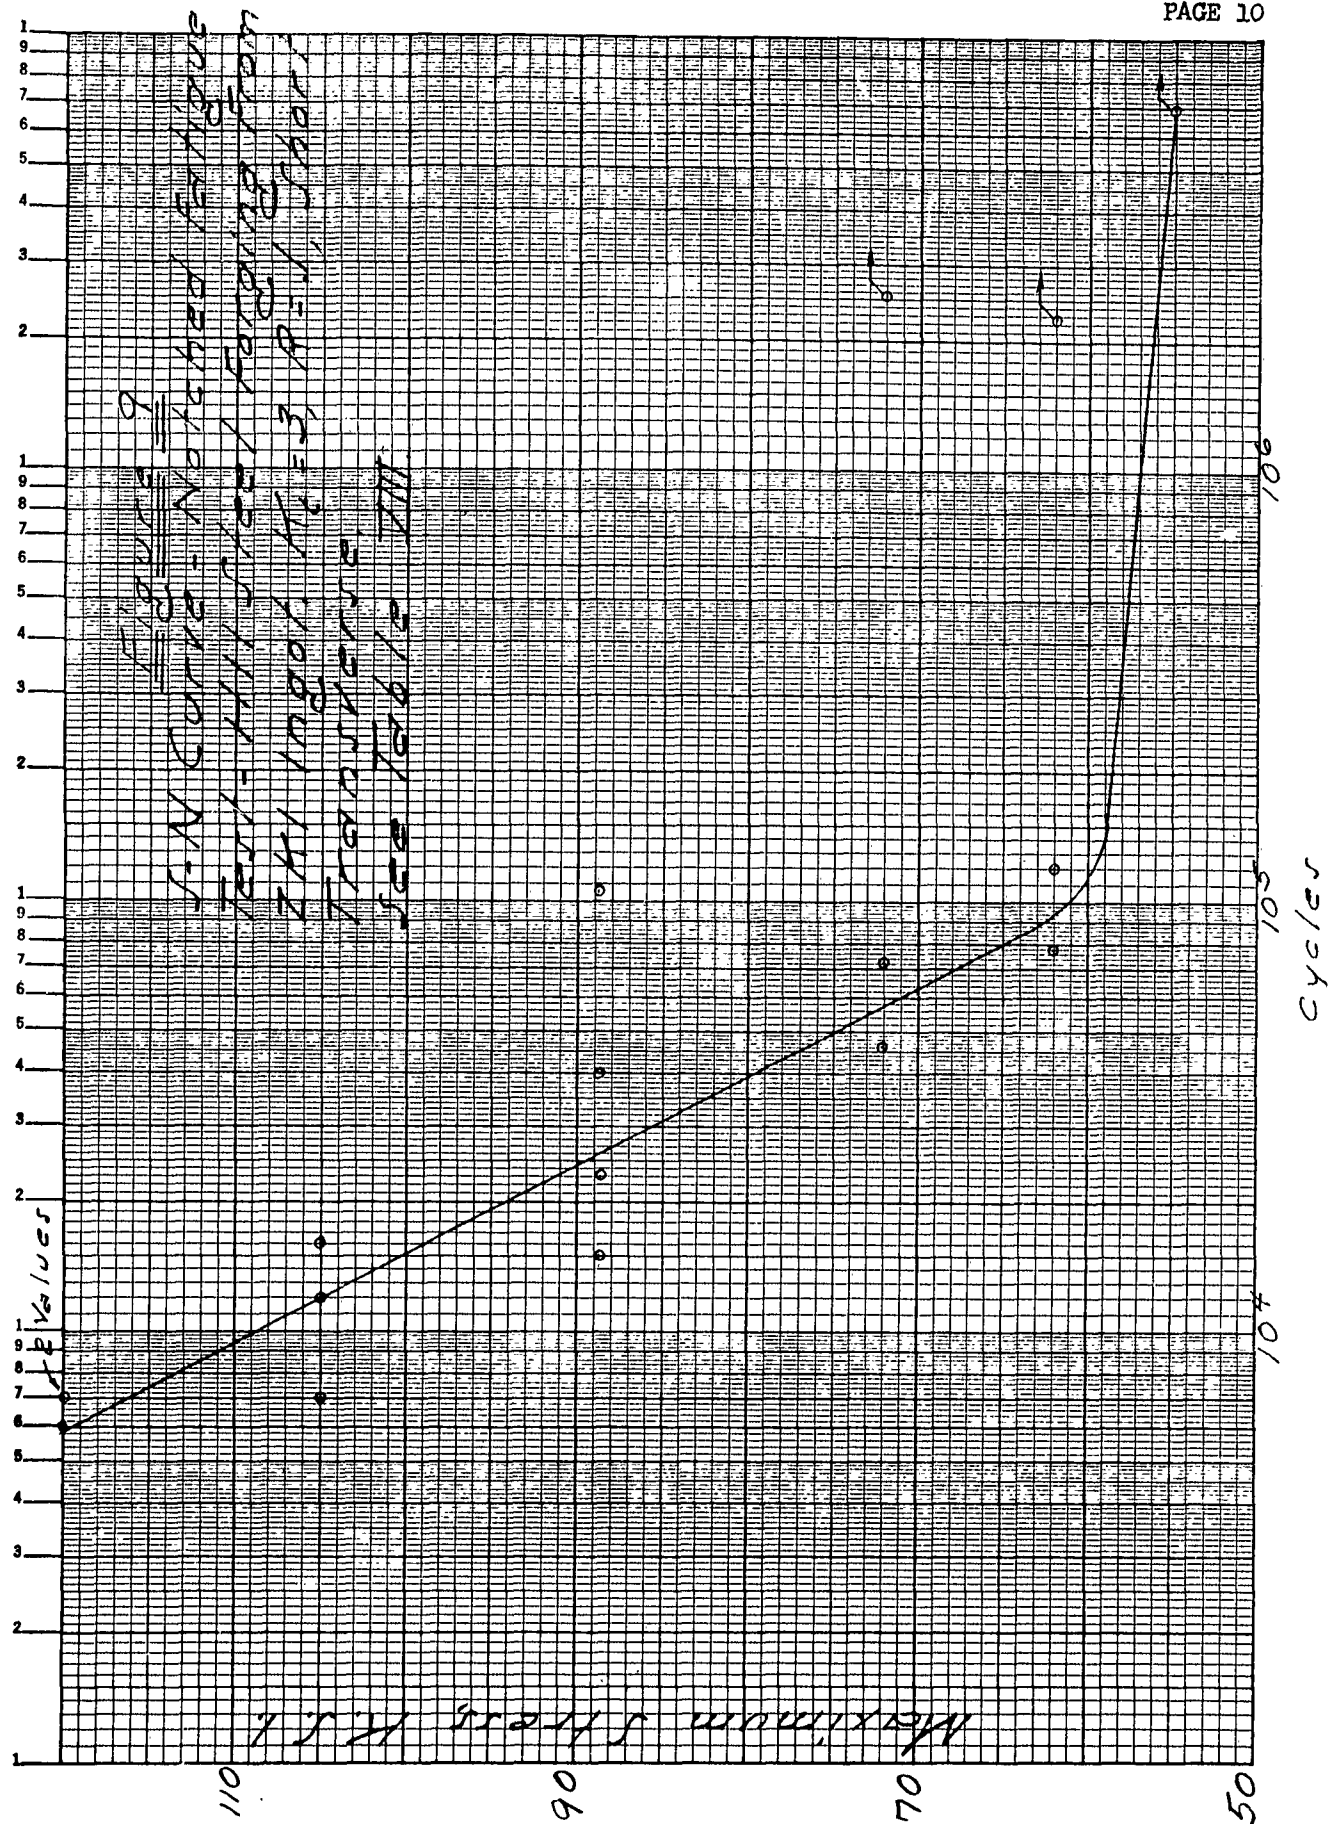

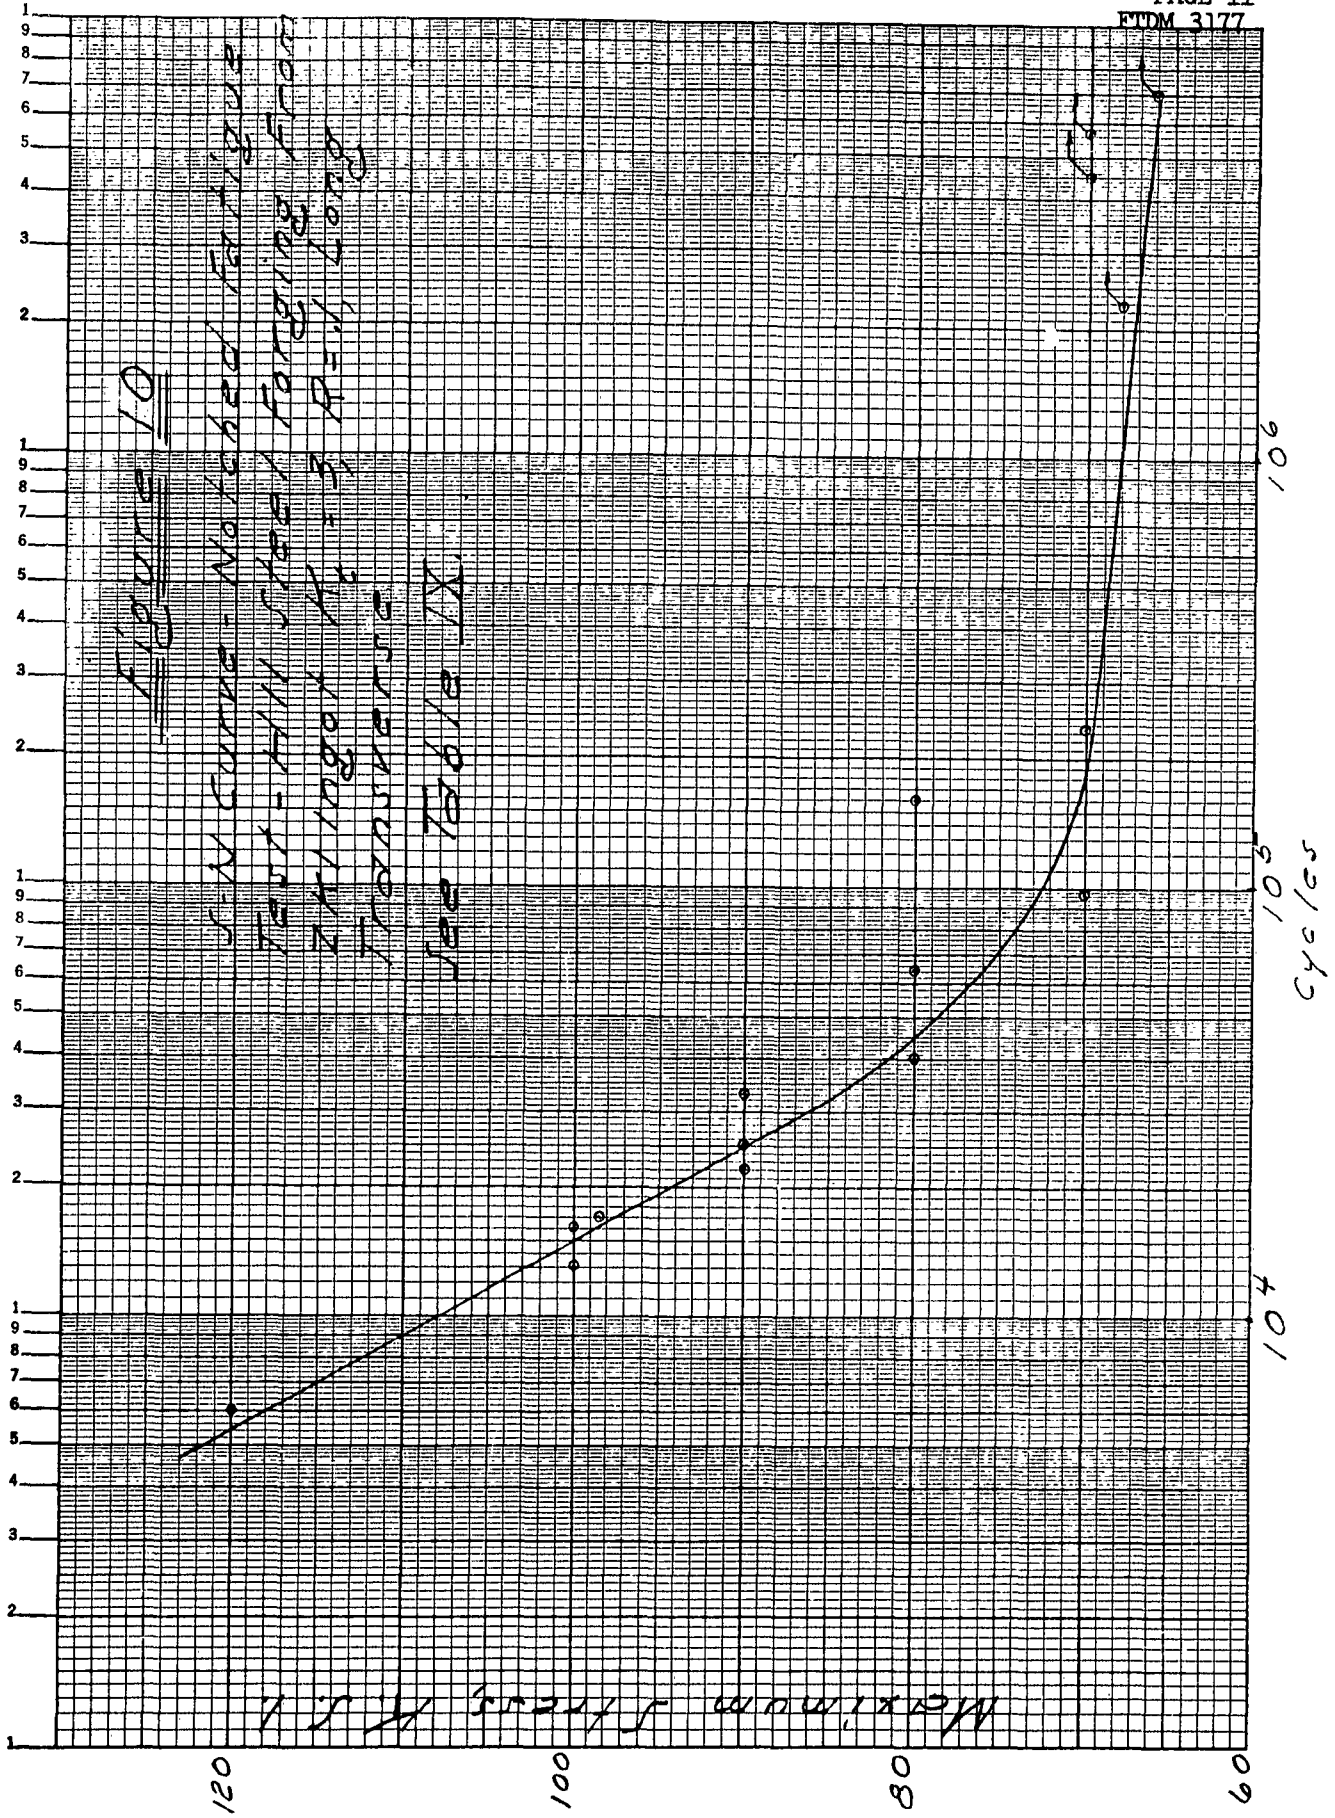

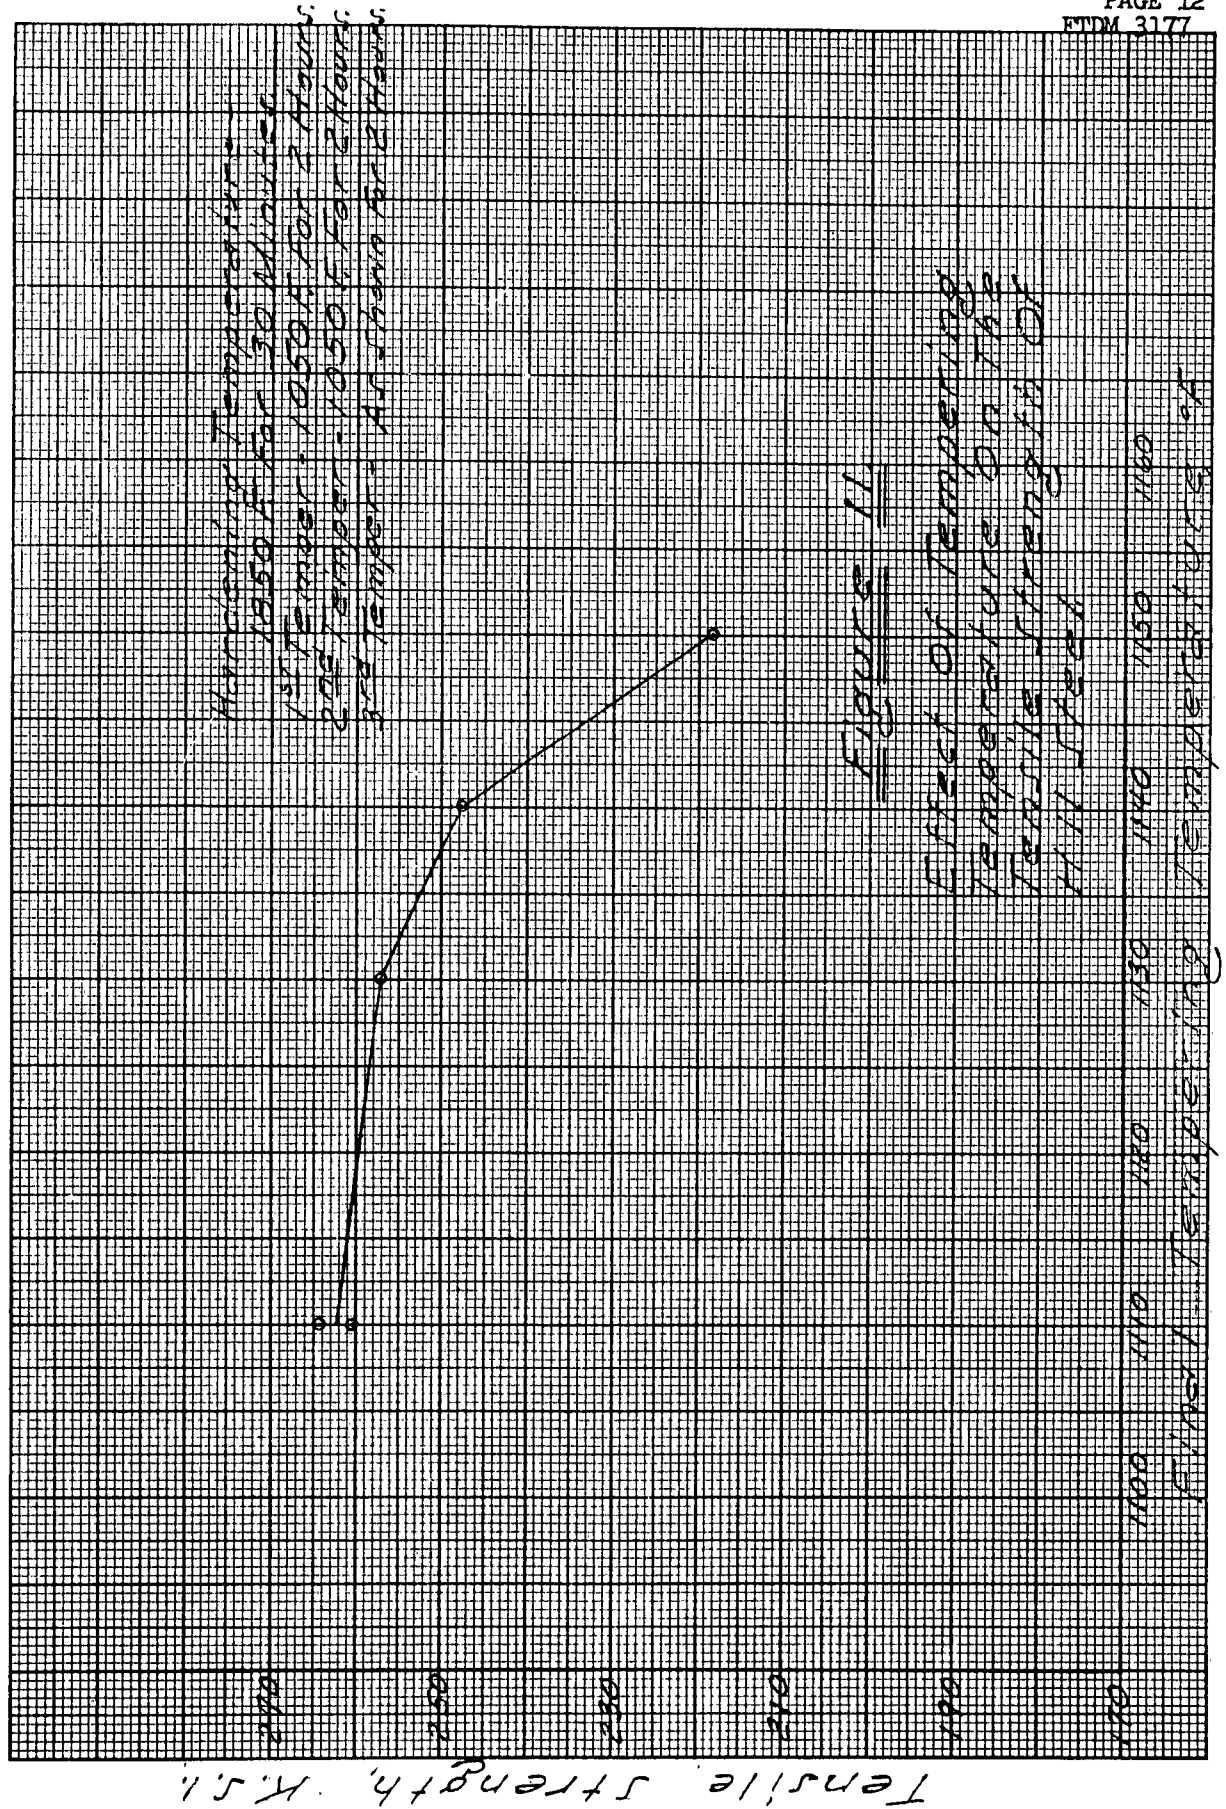

Tensile Strength, K.S.I.

Figure 12

Effect of Time At Tempering Temp-
erature On The Tensile Properties
Of Vacuum Melted $\frac{1}{2}$ H-11 Steel Bars


— Yield Strength
— Tensile Strength

See Table XIII For Heat Treatment

Yield & Tensile Strength, KSI

Low Values
Not Averaged

Hours At Final Tempering Temperature of 1100°F

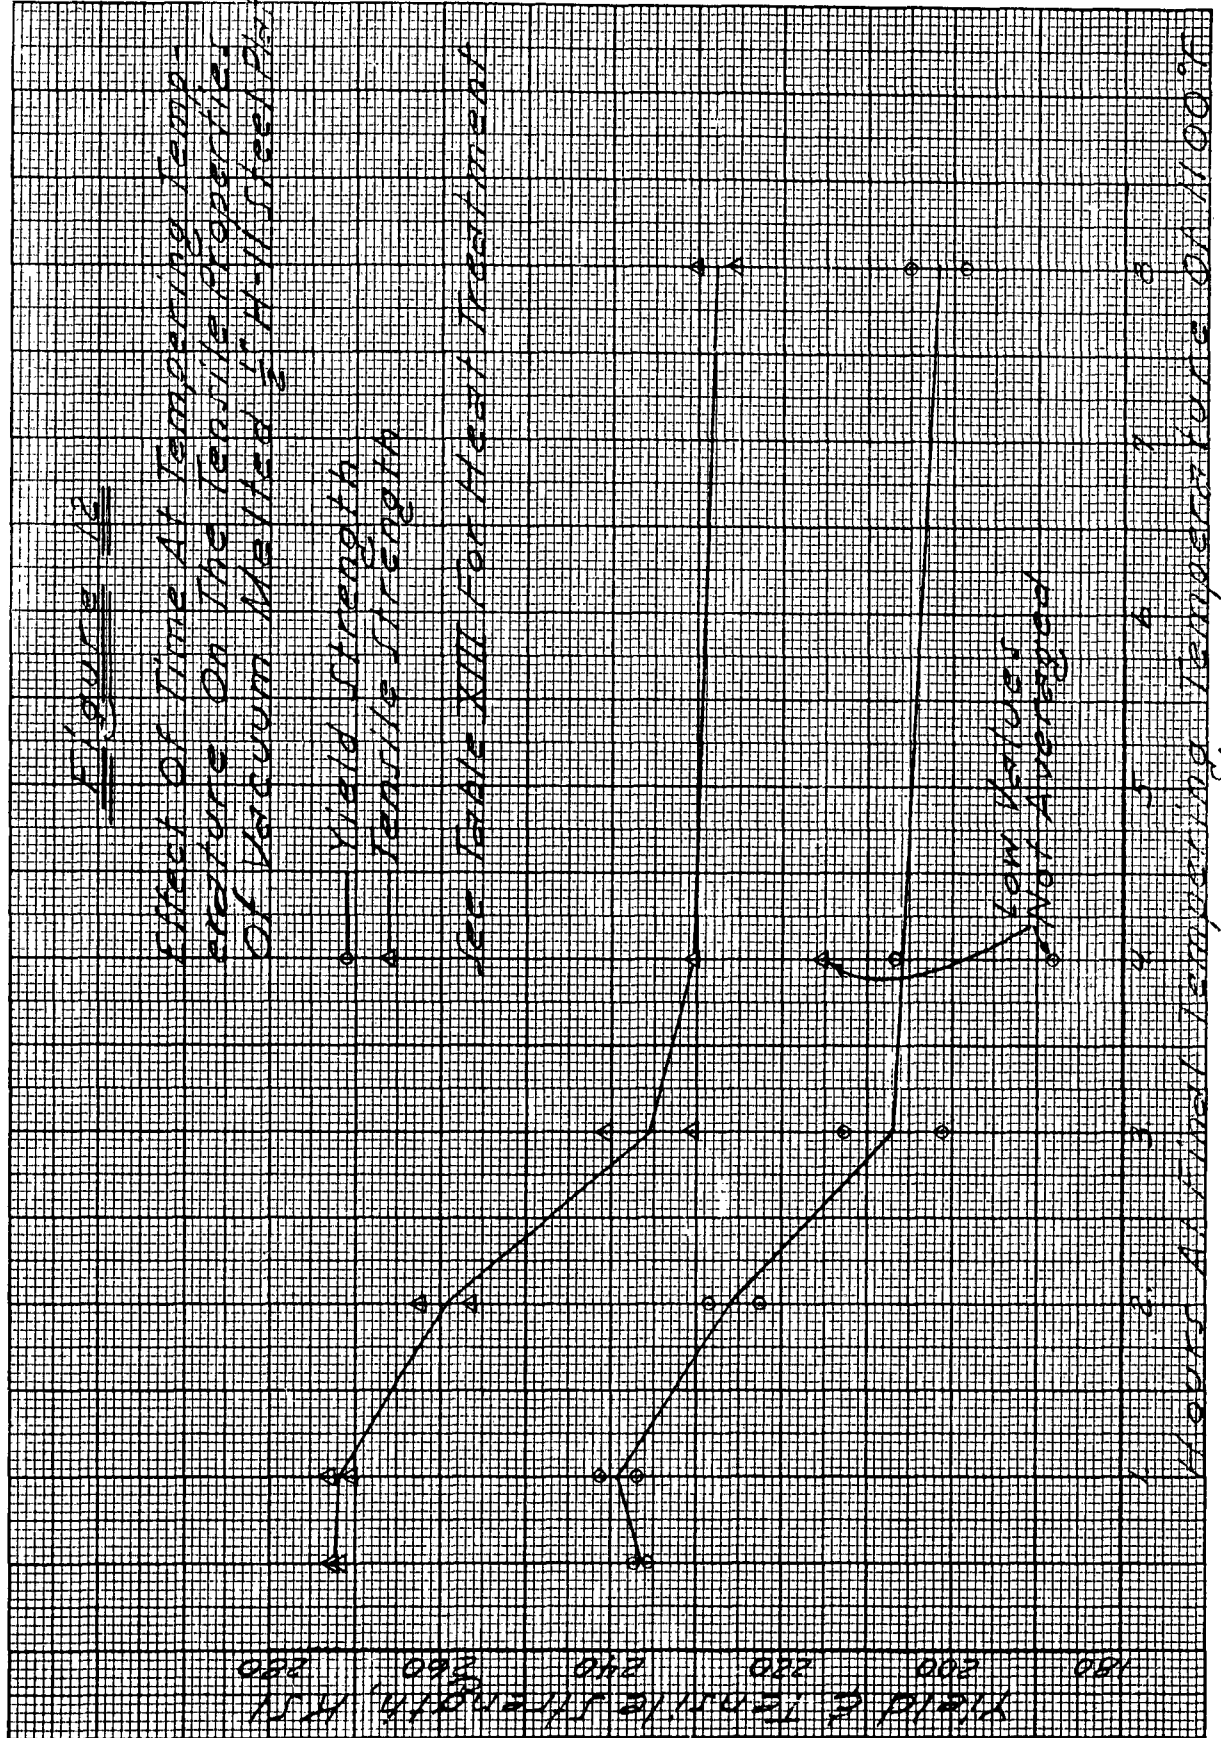

REVISÉD BY _____

GENERAL DYNAMICS | FORT WORTH.

He
Con

** Forged From 8" ACS By Kropp For

Dept. 6
EW 499 11.41

CONVAIR—FORT WORTH

TABULATION SHEET:

TABLE II

Welding Data - Preparation Of Welded Test Specimens From $\frac{1}{2}$ " H-11 Vac. Melted Steel Plate

Equipment - Mechanized T. I. G. Welding Machine.

Electrode - 2% Thoriated Tungsten, $\frac{1}{8}"$ ϕ , Point Ground T_3
60° Included Angle - #8 Ceramic Cup.

Shielding Gas - Argon, 25 cfh On Face, 15 cfh On Root.

Head Travel - $3\frac{1}{2}$ inches Per Minute.

Preheat & Interpass Temperature - 300 To 400° F.

Filler Wire - $\frac{1}{16}"$ Diameter H-11 Steel.

Number Of Passes Per Weld - 5, As Follows:

1 st Pass -	295 Amps, 10 Volts, 10" Filler Wire / Min.
2 nd Pass -	340 Amps, 10 Volts, 12" Filler Wire / Min.
3 rd Pass -	340 Amps, 10 Volts, 14" Filler Wire / Min.
4 th Pass -	365 Amps, 10 Volts, 17" Filler Wire / Min.
5 th Pass -	450 Amps, 10 Volts, 16" Filler Wire / Min.

Post Welding Treatment - Stress Relieve @ 1250° F
For 2 Hours Immediately Following Welding.

CONVAIR—FORT WORTH

MECHANICAL PROPERTIES OF H11 STEEL
 4" x 12" x 30" BILLET - Vacuum Melted.

TABULATION SHEET TABLE III

Specimen No.	Harden- ing - Temp, °F.	Grain- Direction	1st Temp, °F.	2nd Temp, °F.	3rd Temp, °F.	4TH Temp, °F.	Specimen F _y D ₁₀ mm. Inches	F _T Lbs.	F _T KSI	F _T Lbs.	F _T KSI	% Elong.
3-1A	1850	Transv.	1050	1050	1130	—	.5020	46000	232.4	50900	257.2	6.0
3-1B					1140	—	.5070	45000	222.9	50050	247.7	6.5
3-34A					1150	—	.5037	38600	193.7	43500	218.3	9.0
3-34E					1110	—	.5021	46600	235.4	51500	260.1	7.0
3-34H					1110	—	.5062	47700	237.0	53200	264.3	6.0
3-34F					1110	1130	.5087	41100	202.2	47100	231.7	10.5
3-34D					1110	1125	.5076	42300	209.0	47400	234.2	7.0
3-34G					1110	1125	.5051	40800	203.6	46000	229.5	9.0
3-34B					1110	1140	.5039	38600	193.6	43100	216.2	11.0
3-34C					1110	1140	.5046	39700	198.5	43800	219.0	10.5
*	Hardening Temperatures & All Tempering Treatments Were 30 Minute Duration, # 3-25											
Δ	Controls For Fracture Toughness Specimens # 3-15											
○	Controls For Fracture Toughness Specimens # 3-15											

FTDM 3177

PAGE 17
FTDM 3177

TABLE V. Mechanical Properties of H11 Steel - $\frac{1}{2}$ " Plate, Transverse Welded.

Specimen No.	Width, in.	Thick, in.	Area, sq. in.	F _{TS}	F _{TS}	F _{TS}	F _{TS}	F _{TS}	% Elong. 2" G.L.
H3-8	4965	249	1236	25800	2087	28550	2310		5.0
H3-9	508	251	1275	26650	2090	29600	2322	8.0	4.5
H6-7	487	246	1198	24900	2078	26800	2237		5.0
H8-1	501	250	1253	24050	1919	26650	2127		5.0
H9-5	5005	236	1176	25400	2160	28250	2402		3.0
H10-9	497	243	1208	25700	2127	28550	2363	6.0	3.5
H11-8	499	2505	1250	26600	2128	29400	2352	6.0	3.5

Heat Treatment:

Austenitizing: 1850 F 30 Min. Air Cool -
Cool To Below 1300 F. in 3 Minutes.

1st Temper: 1075 F 2 Hrs.

2nd Temper: 1075 F 2 Hrs.

3rd Temper: 1110 F 3 Hrs.

Fatigue Properties Of Hll Steel-
Welded $\frac{1}{2}$ " plate-Vacuum Melted.
T. R = 1 Transverse Welds.

CONVAIR—FORT WORTH

TABULATION SHEET

Specimen No.	Thickness, Inches	Width, Inches	Max. Stress, K.S.I.	Cycles $\times 10^3$	Remarks.
H 7-7	.237	.500	180.	19.	Failed Out of Reduced Section.
H 7-3	.2525	.500	180.	29.	Bearing Failure.
H 9-7	.247	.501	180.	28.	
H 11-6	.251	.501	180.	42.	Bearing Failure.
H 8-9	.211	.497	162.	555.	
H 9-6	.2416	.4785	160	32.	Defective.
Notes: See Table II For Welding Data.					
See Table II For Heat Treatment.					

CONVAIR—FORT WORTH
TABULATION SHEET

TABULE VII

Notch Fatigue Test Results—
4111 Steel Plate, 1" x 12" x 48",
R = .1, Transverse.

Specimen No.	Notch Dia.	Notch Radius	Max. Stress	Cycles	Remarks
	Inches	Inches	ksi	x 10 ³	
T-3.	.2528	.005	110.		Failed in Tension.
T-13.	.2527	.005	110.		Failed in Tension.
T-24.	.2535	.004	110.		Failed in Tension.
T-2.	.2495	.005	100.	9.	
T-11.	.2520	.005	100.	8.	
T-19.	.2545	.005	100.	9.	
T-1.	.2487	.005	80.	23.	
T-5.	.2520	.005	80.	14.	
T-10.	.2530	.0045	80.	14.	
T-15.	.2535	.0045	80.		Failed in Tension
T-8.	.2520	.004	70.	21.	
T-16.	.2525	.005	70.	41.	
T-25.	.2535	.0045	70.	37.	
T-4.	.2520	.005	60.	87.	
T-7.	.2530	.005	60.	107.	
T-9.	.2510	.004	60.	45.	
T-14.	.2520	.005	60.	33.	
T-6.	.2520	.005	50.	169.	
T-12.	.2535	.005	50.	186.	
T-21.	.2520	.0055	50.	1959.	Did Not Fail.
T-18.	.2510	.005	40.	7165.	Did Not Fail.

Notes: See Table VI For Heat Treatment

Notch Fatigue Test Results - H11
Steel Forging From Z H1 Ingot
TABULATION SHEET **TABLE VIII** $H_c = 3$, $R = 1$, Short Transverse.

Specimen No.	Notch Diam.	Notch Radius	Max. Stress	Cycles	Remarks
	Inches	Inches	ksi	$\times 10^3$	
VE 15	.251	.013	120	6	
WE 10	.247	.014	120	7	
WE 7	.250	.014	120	7	
VE 6	.2485	.013	105	12	
WE 5	.247	.014	105	7	
VE 11	.251	.014	105	16	
WE 11	.2505	.014	88	15	
WE 13	.249	.014	88	23	
WE 8	.249	.014	88	40	
VE 8	.249	.014	88	105	
WE 9	.250	.013	72	46	
VE 13	.252	.013	72	73	
VE 14	.250	.014	72	2527	Did Not Fail
VE 16	.2495	.014	62	78	
VE 19	.248	.014	62	120	
WE 3	.251	.014	62	2247	Did Not Fail
VE 1	.250	.014	55	6933	Did Not Fail

Note: Steel Was Vacuum Melted.

See Table II For Heat Treatment

TABLE IX

Notch Fatigue Test Results - H11
Steel Forging From Z H1 Ingot,
 $H_t = 3$, R.R. Long Transverse

Specimen No.	Notch Diam.	Notch Radius	Max. Stress	Cycles	Remarks
	Inches	Inches	ksi	$\times 10^3$	
WC-11	.252	.012	120		Failed on starting.
WC-9	.252	.012	120	6	
WC-6	.251	.013	100	13	
WC-12	.246	.013	100	16	
WC-7	.253	.012	98.5	17	
WC-17	.254	.014	90	25	
WC-4	.252	.014	90	22	
WC-5	.251	.014	90	33	
WC-8	.252	.013	80	64	
WC-7	.251	.014	80	159	
WC-8	.252	.0135	80	40	
WC-6	.249	.013	70	233	
WC-2	.252	.014	70	5616	Did Not Fail.
WC-4	.2475	.012	70	4455	Did Not Fail.
WC-16	.251	.013	70	96	
WC-14	.246	.013	68	2244	Did Not Fail.
WC-8	.257	.014	66	6878	Did Not Fail.

Note: Steel Was Vacuum Melted.

See Table II For Heat Treatment

TABLE X.

Notch Fatigue Test Results—
 H11 Steel Forging, ZHB Ingot—
 $K_t = 5$, $R = 1$, Longitudinal

Specimen No.	Notch Dim.	Notch Radius	Max. Stress	Cycles	Remarks
	Inches	Inches	KSI	$\times 10^3$	
XA-10.	.2475	.005	100.	8.	
XA-2.	.252	.005	100.	6.	
XA-18.	.249	.005	72.	20.	
XA-6.	.249	.006	72.	43.	
XA-16.	.250	.005	72.	32.	
XA-9	.250	.006	50	4347	Did Not Fail.
Note: Steel Was Vacuum Melted.					
See Table II For Heat Treatment.					

CONVAIR—FORT WORTH

TABULATION SHEET

TABLE XIII.

Effect of Time At Tempering Temp.
perature On The Tensile Properties Of
Vacuum Melted $\frac{1}{2}$ " H-11 Steel Plate.

Specimen No.	Grain Direction	Thick Temp. of F.	Thick Temp. Hours	Diam. Inches	F _{TS} Lbs	F _{YS} KSI	F _{TS} Lbs	F _{YS} KSI	F _{TS} Lbs	F _{YS} KSI	% Elong. 2" gage
1	Long.	1100	$\frac{1}{2}$	.2544	12000	235.8	13840	271.9			12.0
2			$\frac{1}{2}$	.2532	11960	237.3	13740	272.6			12.0
3			1	.2513	11960	241.1	13540	273.0			11.0
4			1	.2531	11920	237.0	13600	270.4			12.0
5			2	.2538	11560	228.5	13260	262.1			13.0
6			2	.2540	11280	222.5	13000	256.4			13.0
7			3	.2518	10600	212.9	11980	240.6			13.0
8			3	.2521	10040	201.2	11500	230.5			14.0
9			4	.2521	10320	206.8	11500	230.4			12.0
10			4	.2531	9460	188.1	10820	215.1			15.0
11			8	.2513	9860	198.8	11200	225.8			16.0
12			8	.2536	10360	205.1	11620	230.1			18.0
Heat Treatment:											
Austenitizing - 1850°F - 30 Minutes - Air Cool											
First Temper - 1075°F - 2 Hours.											
Second Temper - 1075°F - 2 Hours.											
Third Temper - As Listed Above.											