

UNCLASSIFIED

AD. 461705L

DEFENSE DOCUMENTATION CENTER

FOR


SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION ALEXANDRIA, VIRGINIA



UNCLASSIFIED

DISCLAIMER NOTICE

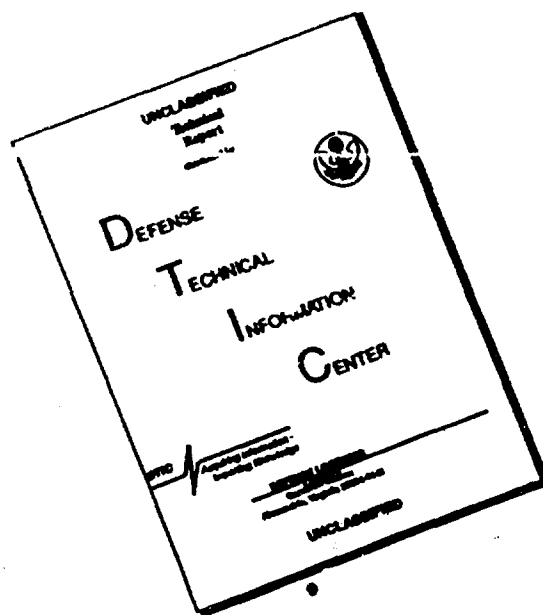

THIS DOCUMENT IS BEST QUALITY AVAILABLE. THE COPY FURNISHED TO DTIC CONTAINED A SIGNIFICANT NUMBER OF PAGES WHICH DO NOT REPRODUCE LEGIBLY.

SSC-167

Fourth Progress Report
of
Project SR-158
"Macrofracture Fundamentals"

to the
Ship Structure Committee

RESTORATION OF DUCTILITY OF HOT OR COLD STRAINED
ABS-B STEEL BY HEAT TREATMENT AT 700 TO 1150°F

by

C. Mylonas and R. J. Beaulieu

Brown University
Providence, Rhode Island

under

Department of the Navy
Bureau of Ships Contract NObs 98294

Washington, D. C.
National Academy of Sciences-National Research Council
April 1965

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

SHIP STRUCTURE COMMITTEE

MEMBER AGENCIES:

BUREAU OF SHIPS, DEPT. OF NAVY
MILITARY SEA TRANSPORTATION SERVICE, DEPT. OF NAVY
UNITED STATES COAST GUARD, TREASURY DEPT.
MARITIME ADMINISTRATION, DEPT. OF COMMERCE
AMERICAN BUREAU OF SHIPPING

ADDRESS CORRESPONDENCE TO:

SECRETARY
SHIP STRUCTURE COMMITTEE
U. S. COAST GUARD HEADQUARTERS
WASHINGTON 25, D. C.

April 1965


Dear Sir:

In order to study the effect of gross strain upon the mechanical and metallurgical properties of steel and to relate these variables to steel embrittlement, the Ship Structure Committee is sponsoring a project at Brown University entitled "Macrofracture Fundamentals." Herewith is a copy of the Fourth Progress Report, SSC-167, Restoration of Ductility of Hot or Cold Strained ABS-B Steel by Heat Treatment at 700 to 1150°F by C. Mylonas and R. J. Beaulieu.

The project is conducted under the advisory guidance of the Ship Hull Research Committee of the National Academy of Sciences-National Research Council.

Comments on this report would be welcomed and should be addressed to the Secretary, Ship Structure Committee.

Sincerely yours,



John B. Oren
Rear Admiral, U. S. Coast Guard
Chairman, Ship Structure Committee

ABSTRACT

The severe embrittlement caused by a suitable history of strain and temperature has been confirmed also for steel conforming to ABS-B classification. Steel prestrained in compression by about 50% at 70 F and subsequently tested in tension fractures at an extensional strain of the order of 1%. Prestraining at 550 F by even 25% can cause brittleness in extension at -16 F. Local severe embrittlement of this nature has been shown to be the basic cause of the static initiation of brittle failure of structures at low average stress. This is confirmed by service failures, whose origin is frequently traced to cold worked areas, or to the hot strained regions of defects close to welds.

It is shown that a suitable heat treatment can restore appreciable ductility to steel embrittled by hot or cold straining. The duration of heating decreases with the temperature, but increases very rapidly with the amount of prestrain. To each temperature corresponds a limiting prestrain for which heat treatment becomes impractically long. Cold strained steel requires considerably longer heat treatment and higher temperatures (1000-1200 F) than hot strained steel (700-1000 F). Approximate time-temperature-prestrain curves have been experimentally determined.

The results confirm that a major beneficial effect of the so-called "thermal stress-relieving" treatment is a restoration of the ductility of locally embrittled steel.

CONTENTS

	<u>Page</u>
1. INTRODUCTION	1
2. EXHAUSTION LIMITS OF ABS-B STEEL	2
2a. Material	2
2b. Testing Method	2
2c. Warm Prestraining	4
3. RESTORATION OF DUCTILITY BY HEATING	6
3a. Heat Treating Procedure	6
3b. Description of the Tests	7
3c. Test Results	7
3d. Tentative Explanation of the "worst" Prestraining Temperature	9
4. CONCLUSIONS	17
REFERENCES	19

INTRODUCTION

The understanding of the mechanism of brittle fracture of structures was greatly advanced by the fundamental observations of Wells (1,2) and the analysis of Drucker (3), which related the overall static behavior of a structure to the amount of plastic deformation at the most severely strained region. Typically brittle failures under static central loading are those occurring before the incidence of general yielding of the cross-section, when the plastic strains at the root of cracks or notches are relatively small and the average stress smaller than yield. Conversely a ductility smaller than needed at the roots of cracks or notches when general yielding begins, should cause fracture at an average stress level lower than yield, hence brittle fractures. Ordinary structural steels tested in the laboratory, however, had been found to have sufficient ductility so as to avoid low static stress fracture in spite of cracks and a low temperature. Consequently, it became clear that service fractures occurring under static loading at low average stress indicated a loss or reduction of the initial ductility of structural steel in the regions of cracks or notch roots. This has been experimentally verified by deliberately damaging the steel so as to reduce its ductility at the notch roots in order to obtain fractures at low average stress. The reduction of ductility was achieved in the laboratory by prestraining notched plates in compression. (4-6) When subjected to subsequent tension these essentially unwelded plates fractured at an average net stress as low as 10% of yield. Extensive research (4-16) with prestrained notched plates, bent beams, and axially compressed bars, has shown that the ductility of steel depends on the whole history of prior strain and temperature, and may be drastically exhausted by cold straining of a closely determined amount, and far more easily by straining at about 500-600°F. The exhaustion of ductility caused

by suitable straining appears as a major factor in the mechanism of static brittle fracture initiation. This is in striking agreement with the general finding that service failures are initiated in cold-worked regions or at defects close to welds, where complex hot straining occurs.

Brittle fracture initiation close to welds was first simulated in the laboratory by Greene (19) with plates butt-welded along edges containing prepared notches. Similar tests were systematized by Wells (1,2,20) and with many variations by several other investigators (21-30). The early cracks and failures of these plates have been mostly attributed to the strong longitudinal residual tension of the thermally contracting region adjacent to the weld. A strong argument in favor of this view has been the prevention of fracture by the so-called "thermal stress-relieving" operation which consists of heating to about 1200°F. Nevertheless, opinions vary widely on the subject of the influence of residual stresses (6,13,18,30,31). With our present knowledge it is readily seen that the local embrittlement resulting from the complex hot straining during the welding cycle is the most likely cause of the test plate failures at the welded-over notches, and of service failures originating close to welds (12).

Increasing attention has been given in the last years to the importance of the embrittlement caused by the history of strain and temperature, particularly in the vicinity of welds (18,25,26,32). The change of ductility of the parent plate near a weld has been confirmed by hardness measurements (33), and by tension (34) and impact tests (35) of notched specimens taken at various distances from the weld. A number of independent investigators starting from different points of view have studied various aspects of the influence of the history of strain and temperature on the properties of steel (36-56). Notable among these is the work of Körber, Eichinger, and Möller, (36) which had escaped the attention of all subsequent investigators.

If the cause of the failures originating at discontinuities near welds or in cold

worked regions is the embrittlement caused by hot or cold straining, the highly beneficial effect of the so-called "thermal stress relieving treatment" should be a restoration, at least in part, of the ductility of the steel. "Mechanical stress relieving" (21,41) may also restore some ductility as shown by instances of strain-softening (39,40). Heat treatment at temperatures higher than 1100-1200°F is employed after forming or spinning.

Lagasse and Hoffmans (45-47) have confirmed that steel sheet embrittled by cold forming could be made sufficiently ductile by heating at about 1100 F, i.e. at the stress relieving temperature. A small number of preliminary tests (15) with E-, ABS-C and A-7 type steel embrittled by cold compression supported this view.

The purpose of the present tests is to study the relation between the required duration and temperature of heat treatment and the amount and temperature of prestrain. Besides their practical usefulness

for "stress relieving", the results could give some indication on the nature of the processes involved in the restoration of ductility and on the physical causes of the initial embrittlement. The precision of the tests depended on the ability to produce controlled embrittlement, and to heat rapidly to the desired temperature so as to avoid significant influences of the intermediate temperatures. Controlled prestrain was effectively produced with the reversed bent test. The rapid heating was achieved by immersion in a lead bath.

2. EXHAUSTION LIMITS OF ABS-B STEEL

2a. Material. The bars used in all tests were cut in the direction of rolling from 3/4 in. plates conforming to ABS Class B specifications, of the same heats as plates tested at the National Bureau of Standards. Composition and properties are shown in Tables I and II.

2b. Testing Method. Exhaustion limits in cold-straining. The reversed bent test

TABLE I. COMPOSITION OF ABS-B STEEL.

	C	Mn	P	S	Si	Ni	Cu	Cr	Al	N
Minimum	0.14	0.91	0.009	0.018	0.041	0.021	0.051	0.023	0.02	0.004
Maximum	0.18	1.07	0.012	0.028	0.056	0.040	0.096	0.031	0.03	0.006
Typical	0.14 0.15	1.04 0.94	0.011 0.009	0.018 0.027	0.056 0.046	0.023 0.040	0.083 0.094	0.031 0.023	0.02 0.02	0.004 0.005

TABLE II. PROPERTIES OF ABS-B STEEL.

	Yield Point ksi	Ultim. Strength ksi	Elong. (8") %	Finish Temp. °F	Ferrite Grain Size	°F			Nil Dugt. Temp. °F Center	Fibrous	
						T _{V10}	T _{V15}	T _{V20}		50% °F	10% °F
Maximum	32.6	57.9	31.0	1600	7.8	-30	-24	-13	-20	24	-22
Minimum	35.7	63.9	33.0	1725	8.2	-5	6	18	-10	39	-10
Typical	33.8 35.7	58.4 59.8	33.0 32.0	1640 1800	7.8 8.1	-5 -11	6 2	18 +11	-10 -10	37 28	-14 -15

From 12 analyses and 6 tests by the Nat. Bureau of Standards on pieces taken from plates of the same heat as used in the present tests.

(13,14) was employed throughout the present investigation. Bars of dimensions 9 x 1.00 x 0.75 in. are bent at first slightly in four point loading (Fig. 1a), and then more in longitudinal compression till they buckle and bend by various amounts (Fig. 1b). This is referred to as the prestrain or initial bending. The final test consists of pulling the bars open in a reversed bending action (figures 1c and 2). The compressive prestrain ϵ_o at the intrados (which is one of the as-rolled surfaces of the steel plate) is calculated from the radius of curvature R and the bar thickness h

$$\epsilon_o = h/(2R+h)$$

As was found with tests of other steels, bars prestrained above a certain limit are brittle and fracture in reverse bending at small strains and low loads. Bars prestrained below this limit have sufficient ductility so as not to fracture even when pulled open by large amounts, corresponding to large extensional strains and high loads. The prestrain causing the sudden reduction of ductility is referred to as the exhaustion limit. The great convenience of the reversed-bend tests is the ease with which the exhaustion limit may be determined by simple measurement of the load at fracture. As shown in Figure 3 (right) bars prestrained at 70°F by more than 0.55 (55%) and aged (1 1/2 hours at 300°F) cracked or fractured in subsequent reversed bending at 70°F under loads well below 3000 lb. On the contrary bars prestrained below 0.55 did not break at loads well above 5000 lb. Bars withstanding the arbitrary load of 5000 lb. are called ductile; those breaking at loads below 5000 lb. are brittle. Any other load limit higher than about 3000 lb. would give the same exhaustion limit of 0.55 for these conditions of testing. The exhaustion limit is usually determined within a strain of ± 0.02 or less. For bars prestrained at 70°F, aged and tested at -16°F the exhaustion limit lies between

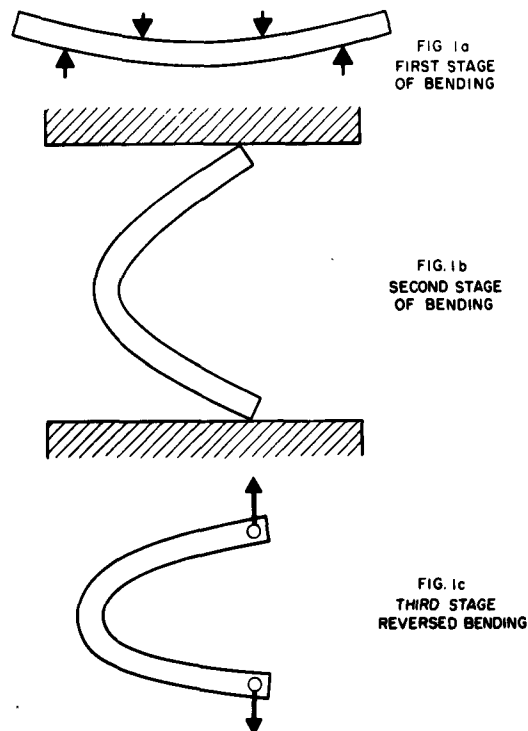


FIG. 1. SCHEMATIC BENT BAR TESTING.



FIG. 2. HORIZONTAL TESTING MACHINE FOR BENT BARS IMMERSSED IN COOLING BATH. (TANK MOVED TO THE LEFT).

0.45 and 0.48 (Fig. 3, left). The detailed results of 62 tests plotted in Figure 3 are given in Table III.

During final testing, all bars were immersed in a liquid bath. This reduced the localized heating caused by plastic work, provided the test was slow, and eliminated the convection heating of bars tested at -16°F. A special horizontal hydraulic testing machine was built for this purpose (Fig. 2). The legs of the U-shaped bars are upright, and the lower curved part hangs inside a cooling tank (moved to the left in Figure 2). Water was used for the tests at 70°F, and glycerine at 60% concentration for the tests at -16°F. Glycerine was not found to affect significantly the results.

The exhaustion limit is a sensitive indicator of the influence of many variables on the embrittlement of steel. A reduction of the exhaustion limit indicates a stronger embrittling action, since a lower prestrain exhausts the ductility to the point of brittleness. An increase of the exhaustion limit indicates a less embrittling action. Thus, aging and low testing temperatures reduce the exhaustion limit.

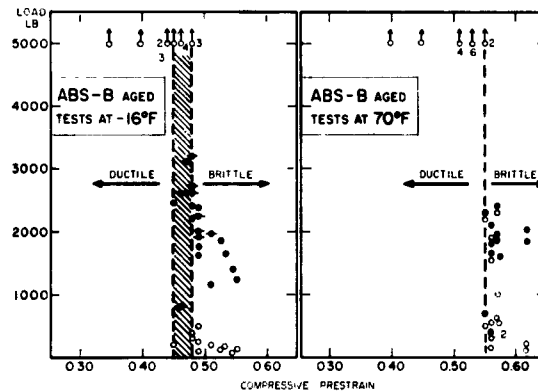


FIG. 3. EXHAUSTION LIMITS OF ABS-B STEEL INITIALLY BENT AT 70° AND AGED.

2c. Warm prestraining. As discussed elsewhere (12,15) the easier embrittlement caused by straining at about 500 to 600°F is related with the initiation of brittle fracture at defects close to welds. The most embrittling temperature and the corresponding reduced exhaustion limit may prove useful indications of how prone a steel is to such embrittlement.

Bars were prestrained at various temperatures up to 850°F. After heating in

TABLE III. EXHAUSTION LIMIT OF BARS OF ABS-B STEEL PRESTRAINED AT 70° AND AGED.

Strain	TESTS AT -16°F		Strain	TESTS AT 70°F	
	Test Load (lb.)			Test Load (lb.)	
	Arr. Crack	Fracture		Arr. Crack	Fracture
.35		*	.40		*
.40		*	.45		*
.45		*	.51		*
.45		*	.51		*
.45		*	.51		*
.45		*	.51		*
.45	200	2450	.51		*
.46		*	.51		*
.46		*	.51		*
.46		*	.51		*
.46		*	.53		*
.46		2600	.53		*
.46		*	.53		*
.46		800	.53		*
.46		3100	.53		*
.47		2600	.55	500	700
.48		3200	.55		*
.48	300	2400	.55	2200	2300
.48		*	.56	300	1800
.48		2600	.56	1550	1650
.48		*	.56	150	400
.48		2700	.56	1800	2100
.48	300	2200	.56	550	1650
.48		*	.56	300	1450
.49		1890	.57	650	1800
.49		1975			
.49	100	2400			
.49	500	1750	.57	550	1600
.49	250	1650	.57	2300	2400
.49		2300	.57	1000	1900
.53	100	1850	.62	200	2060
.53	100	1850	.62	100	1850
.53	100	1440			
.60	100	1290			

* No fracture at 5000 lb., equivalent to over 80 ksi.

an oven to the required temperature the bars were given the initial four-point bending (Fig. 1a), and after reheating for about 30 min., they were bent to the required radius and left to cool. One or more days later they were tested in reversed bending (Figures 1c and 2) at 70°F or -16°F. The results of 76 tests at 70°F and of 82 tests at -16°F are given in Tables IV a, b and V a, b, and i graph form in Figures 4 and 5, where the temperature of prestrain is plotted against the amount of prestrain, and the behavior of the bars in subsequent tension is marked by a black circle when brittle, and by an open circle when ductile (i.e. when no fracture had occurred under 5000 lb. or more). A "worst" temperature range exists around 550°F, for bars tested at 70° as well as -16°F.

TABLE IV (b)

BAR	INITIAL BEND		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi
	Strain °F		App. Crack	Fracture	
B 10	0.43	300		*	*
B 11		300		*	*
B 22		400		2060	48.8
B 23		400		*	*
B 74		500		1650	3900
B 75		500		1030	2080
B 24		700		1450	1650
B 25		700		2080	48.6
B 40		750		1750	40.4
B 41		750		1854	43.4
B 12		800		*	*
B 13		800		*	*
B 60		0.48	250		*
B 61	250			*	*
B 44	300			620	1130
B 45	300			*	*
B 64	400			1030	1650
B 65	400			1440	2060
B 72	550			210	1030
B 73	550			210	1030
B 78	700			1030	2690
B 79	700			3710	*
B 30	800			*	*
B 31	800			2680	59.6
B 62	850			*	*
B 63	850		*	*	
B 20	0.54	250		3500	-
B 21		250		1130	2060
B 86		400		210	1440
B 87		400		820	1850
B 76		850		1850	3300
B 77		850		2880	*
B 50		1000		*	*
B 51		1000		*	*

* No fracture at 5000 lb., equivalent to over 80 ksi.

TABLE IV (a) and (b).

EXHAUSTION LIMIT OF BARS OF ABS-B STEEL
PRESTRAINED HOT AND TESTED AT 70° F.

BAR	INITIAL BEND		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi
	Strain °F		App. Crack	Fracture	
B 6	0.23	500		*	*
B 7		500		*	*
B 46	0.24	550		*	*
B 47		550		*	*
B 4	0.27	450		*	*
B 5		450		*	*
B 14		550		3510	*
B 15		550		*	*
B 1		650		*	*
B 2		650		*	*
B 52	0.30	450		*	*
B 53		450		*	*
B 48		550		3510	77.5
B 49		550		*	*
B 54		650		*	*
B 55		650		*	*
B 32	0.33	450		*	*
B 33		450		2060	45.4
B 16		550		*	*
B 17		550		1650	-
B 68		550		1440	*
B 69		550		2100	43.6
B 34		650		*	*
B 35		650		*	*
B 8		700		*	*
B 9		700		*	*
B 42	0.35	550		2080	45.8
B 43		550		*	*
B 38	0.37	400		*	*
B 39		400		2890	-
B 28		450		2060	-
B 29		450		2060	48.6
B 70		550		1030	2270
B 71		550		820	1650
B 58		550		1240	1650
B 59		550		1650	2060
B 26		650		1130	1440
B 27		650		1130	1440
B 36		700		3090	-
B 37		700		1650	77.4
B 56		800		*	*
B 57		800		*	*

* No fracture at 5000 lb., equivalent to over 80 ksi.

TABLE Va.

EXHAUSTION LIMIT OF BARS OF ABS-B STEEL
PRESTRAINED HOT AND TESTED AT -16° F.

BAR	INITIAL BEND		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi	
	Strain °F		App. Crack	Fracture		
B 058	0.20	550		*	*	
B 059		550		*	*	
B 046	0.22	550		4330	81.5	
B 047		550		4540	82.4	
B 06	0.23	500		*	*	
B 07		500		4950	75.0	
B 048		550		1850	-	
B 049		550		3920	78.7	
B 056		600		*	*	
B 057		600		4540	85.5	
B 038		0.24	400		*	*
B 039	400			*	*	
B 030	450			3720	70.7	
B 031	450			2270	49.0	
B 052	550			3510	70.0	
B 053	550			1850	34.8	
B 032	650			1650	-	
B 033	650			3510	70.0	
B 036	700			*	*	
B 037	700			*	*	
B 060	0.27	400		*	*	
B 061		400		*	*	
B 04		450		870	*	
B 05		450		*	*	
B 062		550		2060	-	
B 063		550		1850	-	
B 02		650		3710	80.7	
B 03		650		3920	83.0	
B 022		700		2480	51.1	
B 023		700		*	*	
B 064		0.30	300		*	*
B 065			300		*	*
B 068			400		2480	-
B 069	400			1850	-	
B 028	450			2370	51.0	
B 029	450			2890	67.0	
B 070	550			1650	-	
B 071	550			1240	-	
B 026	650			1850	46.0	
B 027	650			2680	62.6	
B 040	750			*	*	
B 041	750			3920	87.2	
B 066	800			*	*	
B 067	800			*	*	

* No fracture at 5000 lb., equivalent to over 80 ksi.

TABLE Vb. EXHAUSTION LIMIT OF BARS OF ABS-B STEEL PRESTRAINED HOT AND TESTED AT -16° F.

BAR	INITIAL BEND		TEST LOAD (lb)		FRACTURE STRESS NW/bd ² ksi
	Span	°F	App. Crack	Fracture	
B 072	0.33	300		+	+
B 073		300		+	+
B 074		400		3300	72.8
B 075		400		3920	82.5
B 019		550		2890	56.7
B 019		550		3510	70.9
B 08		700		2060	45.2
B 09		700		3510	79.8
B 034		800		2680	59.4
B 035		800		2890	59.2
B 076	850		+	+	
B 077	850		+	+	
B 044	0.37	300		+	+
B 045		300		2890	68.0
B 020		400	208	1440	-
B 021		400	618	1440	-
B 042		800		3920	85.6
B 043	800		3500	81.5	
B 078	0.40	300		+	+
B 079		300		+	+
B 080		400		1850	43.9
B 081		400		1690	40.9
B 082		550		2890	
B 083		550		2480	
B 012		800		3920	92.0
B 013		800		3500	77.4
B 084		850		+	+
B 085		850		3090	72.5
B 054		900		+	+
B 055		900		+	+
B 016		0.44	250		+
B 017	250			+	+
B 010	300		1130	1650	39.0
B 011	300		1440	1650	38.9
B 086	800		*10	1130	
B 087	800			1850	
B 014	900			3300	79.8
B 015	900			2480	60.0
B 024	1000			+	+
B 025	1000			+	+

* No fracture at 5000 lb., equivalent to over 80 ksi.

The prestrain at the "worst" temperature causing brittleness at 70°F, is just over half the prestrain at room temperature (about 0.32 as compared to 0.55). For tests at -16°F the difference is even more pronounced: the prestrain at the "worst" temperature is less than half that at 70°F (about 0.22 as compared to 0.47).

As the prestrain temperature rises above about 600°F, the exhaustion limit increases again, showing a weaker embrittling effect. Above about 900° the exhaustion limit is higher than at room temperature.

3. RESTORATION OF DUCTILITY BY HEATING

3a. Heat treating procedure. Preliminary tests have shown (15) that oven heating produces a very slow temperature rise in the bars. Cold bars would reach the oven temperature in about 30 minutes. This long heating time obscured the time-temperature relationship for heat treatment. A more rapid electrical resistance heating was tried. A 2 volt 4000 amp. current from a modified lighting transformer with a single turn secondary

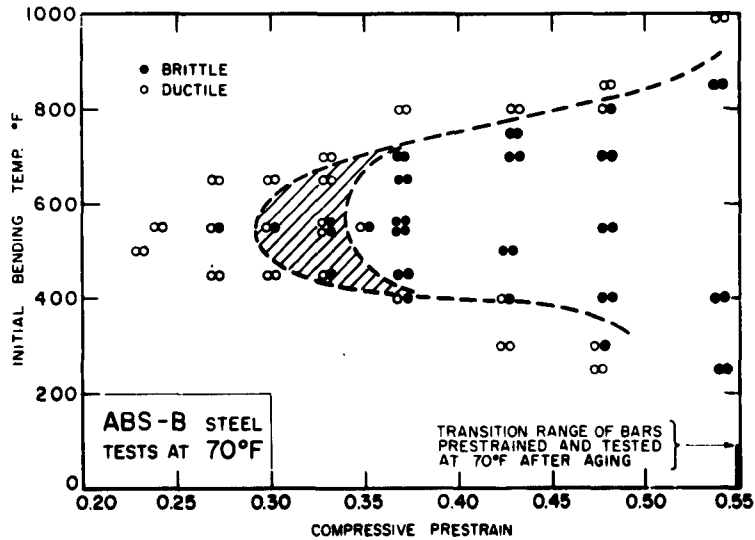


FIG. 4. EXHAUSTION LIMITS OF ABS-B STEEL INITIALLY BENT HOT.

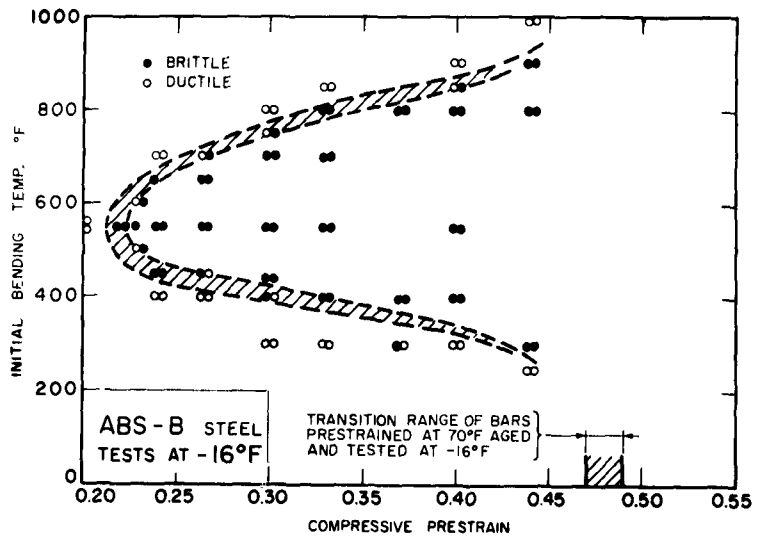


FIG. 5. EXHAUSTION LIMITS OF ABS-B STEEL INITIALLY BENT HOT.

winding was passed through the bent bars held in special clamps. The temperature was measured with thermocouples on the specimens, and was found to reach the desired level in less than 3 minutes, but non-uniform heating resulted, with a hot region at the intrados. The only satisfactory method of uniform and rapid heating was by immersion of the prestrained bars in a commercial lead bath thermostatically controlled to within $\pm 5^{\circ}\text{F}$. The bars were first immersed partially, with the legs of the U-shaped bars in the lead bath and the intrados outside. Three minutes later, when the intrados had been heated to about 100°F below the bath temperature, and the lead bath had recovered its set temperature, the bars were totally immersed, and in two more minutes were within 5 degrees of the bath temperature. This was taken as the beginning of the heat treating period in all tests. The effect of the short heating time below the test temperature is negligible. For example, bars bent cold to a prestrain of 0.55 and tested at -16°F , were made ductile by a heating of about 10 minutes at 1150°F , 20 minutes at 1100°F and not even 2 hours at 1050°F (Figures 8 and 9). The rate of restoration of ductility decreases quite rapidly when

the temperature drops.

3b. Description of the tests. The tests included bars strained at 70°F and at the "worst" temperature of 550°F , and tested after heat treatment at 70° and at -16°F . The bars were prestrained by various amounts above the exhaustion limit for the specific conditions of each test, so that without heat treatment they should have all been brittle. With bars prestrained at 70°F the exhaustion limit was about 0.55 for tests at 70°F , and about 0.45-0.48 at -16°F ; and with bars prestrained at 550°F it was about 0.30-0.35 for tests at 70°F and about 0.21-0.22 for tests at -16°F .

The duration of heat treatment varied from 3 to 120 minutes. Temperatures between 1000 and 1150°F for cold strained bars, and between 700 to 1000°F for hot strained bars were tried.

3c. Test results. The results of 206 tests of cold strained bars and 311 hot strained bars are given in Tables VI to XXII. The results are also plotted in the graphs of Figures 6 to 16, according to temperature of prestrain, of heat treatment, and of test. In these figures the heat treating time

TABLE VI. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1000 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi
		*F	Minutes	Arr. Crack	Fracture	
638	0.56	1000	3	-	2300	+
640			3	-	+	
641			5	-	+	
642			5	-	+	
648	0.57	1000	3	-	4700	+
650			3	-	2600	
637			5	-	+	
638			5	-	+	
639			10	-	+	
636			10	-	+	
643	0.59	1000	15	2500	3050	-
644			15	-	1600	
631			30	-	3100	
632			30	-	+	
633			30	-	+	
634			60	-	4800	
651*	0.60	1000	30	-	2500	+
652*			30	-	2300	
653*			60	-	2600	
654*			60	-	5050	
718*			120	-	2900	
720*			120	-	4900	
675*	0.62	1000	90	-	4690	-
676*			90	-	3100	

+ No fracture at 5000 lb., equivalent to over 80 ksi.
 * Shorter bars. Highest load is 6300 lb., equivalent to over 80 ksi.

TABLE VII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1050 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi
		*F	Minutes	Arr. Crack	Fracture	
697	0.56	1050	3	-	2100	+
698			3	-	1650	
622			5	-	+	
622			5	-	+	
671	0.57	1050	5	-	+	+
672			5	-	4900	
661	0.59	1050	6	-	2700	-
662			8	-	4500	
635			15	-	+	
636			15	1200	1600	
623			30	-	+	
624			30	-	+	
711*	0.60	1050	15	-	6100	+
712*			15	-	5500	
721*			30	-	+	
722*			30	-	3100	
743*			60	-	5770 x	
744*			60	-	5480 x	
751*			90	-	4740	
752*			90	-	3300 x	
757*			90	-	4950	
758*			90	-	4950	
723*	0.62	1050	30	-	5800	-
724*			30	-	5200	
745*			120	-	2680 x	
746*			120	-	2880 x	
677*	0.63	1050	30	-	3100	-
678*			30	-	4700	
683*			60	-	4600 x	
684*			60	-	4700 x	

+ No fracture at 5000 lb., equivalent to over 80 ksi.
 * Shorter bars. Highest load is 6300 lb., equivalent to over 80 ksi.
 x Pre-existing crack, as shown by discolored part of fracture surface.

TABLE VIII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1100 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kN/bd ² ksi
		*F	Minutes	Arr. Crack	Fracture	
609	0.56	1100	3	-	1900	+
610			3	-	+	
605			5	-	+	
606			5	-	2300	
602			10	-	+	
604			10	-	+	
627	0.57	1100	8	-	+	+
628			8	-	+	
615			15	-	+	
616			15	-	+	
607			30	-	+	
608			30	-	+	
667			60	-	+	
668			60	-	+	
665	0.59	1100	8	-	+	+
666			8	-	4500	
625			15	-	+	
626			15	-	4100	
613			30	-	+	
614			30	-	+	
611			60	-	+	
612	60	-	+			
673*	0.60	1100	30	-	3200 x	-
674*			30	-	6100	
703*			30	-	2500 x	
704*			30	-	+	
759*	0.61	1100	60	-	3300 x	-
760*			60	-	4950	
689*	0.62	1100	60	-	4600	88.6
690*			60	-	4900	
717*			120	-	5900	
719*			120	-	+	

+ No fracture at 5000 lb., equivalent to over 80 ksi.
 * Shorter bars. Highest load is 6300 lb., equivalent to over 80 ksi.
 x Pre-existing crack, as shown by discolored part of the fracture surface.

is plotted against the amount of prestrain, which is always higher than the corresponding exhaustion limit shown in the legend. Bars deforming without fracture under a load up to or beyond 5000 lb. are termed ductile and are represented by open circles. Bars fracturing at lower loads are termed brittle and are represented by full circles. To produce prestrains of 0.60 or more (cold strained bars) it was found necessary to shorten the bars, otherwise their legs would touch during bending. These shorter bars are indicated by an asterisk in Tables VI to XII, and were tested to the calculated equivalent load of 6300 lb. It was also found that some of the most highly strained bars had developed cracks before the final test, as was obvious from discolored areas of the fracture surfaces. These bars are marked by the sign x and are not taken under consideration.

TABLE IX. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1150 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS MN/bd ² ksi			
		°F	Minutes	Arr. Crack	Fracture				
617	0.57	1150	3		+	+			
618					+	+			
669	0.59	1150	5		+	+			
670					+	+			
629					+	+			
630					+	+			
619					2400	+			
620					+	+			
701 ^a	0.60	1150	5		5800	78.2			
702 ^a					4000 x	-			
781 ^a	0.61	1150	15		2470 x	-			
782 ^a					-	-			
691 ^a	0.62	1150	15		3000	-			
692 ^a					3300	-			
753 ^a					3090	-			
754 ^a					2980	-			
678 ^a					+	-			
680 ^a					+	-			
713 ^a	0.63	1150	30		5800	74.6			
716 ^a					3090 x	-			
755 ^a					3280	71.6			
756 ^a					2800	57.6			
729 ^a					2800 x	-			
730 ^a					2800 x	-			
767 ^a					3190 x	-			
768 ^a					2590	-			
693 ^a				0.65	1150	15		4000	-
694 ^a								5850	57.4
695 ^a		2800	-						
700 ^a		2700	-						
731 ^a		+	-						
732 ^a		+	-						

• No fracture at 5000 lb., equivalent to over 80 ksi.
 * Shorter bars. Highest load is 6300 lb., equivalent to over 90 ksi.
 x Pre-existing crack, as shown by discolored part of fracture surface.

The scatter of the results is considerably greater and the transition from brittle to ductile less sharp than with non heat-treated bars. There are indications that the ductility is restored gradually during heating. Although the loads appear to increase gradually with heating time up to 5000 lb. (or 6300 lb. for the shorter bars), very rarely did fractures occur at the higher loads (up to 7000 lb.) at which the bars were frequently tested. The 5000 lb. (or 6300 lb.) still shows the restoration of an appreciable ductility, with extensional strains well over 0.10.

In spite of scatter, the results indicate an unexpected dependence of the least necessary duration of heating on the amount of prestrain. Approximate curves of the minimum heating time needed to restore the ductility have been plotted as functions of prestrain, except for the heat treating temperature of 850°F. (Fig.

TABLE X. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1000 F & 1050 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS MN/bd ² ksi
		°F	Minutes	Arr. Crack	Fracture	
043	0.49	1000	30		4640	-
044					3090	-
087					4120	92.0
088					2480	71.7
091					3090	74.6
092		120	3090	74.3		
033	0.51	1000	30		2890	-
034					4540	-
045					4740	-
046					2890	-
073					4430	92.4
074		120	3920	62.7		
021	0.55	1000	60		2480	-
022					3090	-
035					4740	-
036					3090	-
063	0.49	1050	3		+	+
064					+	+
051	0.51	1050	3		+	+
052					+	+
067					+	+
048					+	+
037					+	+
038					+	+
023					+	+
024					+	+
093	0.53	1050	8		4430	84.4
094					4540	85.1
085					3300	79.7
086					+	+
081					+	+
082					+	+
077					+	+
078					+	+
025	0.55	1050	60		2480 x	-
026					4540	-
039					4950	-
040					4850	-

• No fracture at 5000 lb., equivalent to over 80 ksi.
 x Pre-existing crack, as shown by discolored part of fracture surface.

14, above), where the scatter was too great. The heating time increases so rapidly with prestrain, that an effective cut-off prestrain appears to exist beyond which restoration of ductility, if at all possible, would not be practical. It is not known whether any deterioration of the steel under prolonged heating contributes to this effect. The collected curves for all straining, heat treating, and testing temperatures are shown in Figure 17. The unexpected dependence of heating time on amount of prestrain, and its expected inverse dependence on heat treating temperature are clearly indicated. This is also shown in Fig. 18 where the approximate minimum heat treating time is plotted against the heat treating temperature for various constant prestrains at 550°F.

3d. A tentative explanation of the "worst" prestraining temperature. A very

TABLE XI. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1100 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS wt/rd ² ksi
		°F	Minutes	App. Crack	Fracture	
041	0.51	1100	3		*	*
042			3		*	*
027			5		*	*
028			5		*	*
05			10		*	*
06	10		*	*		
067	0.53	1100	5		*	*
068			10		3300	*
059			10		*	*
060	10		*	*		
08	0.55	1100	15		4580	*
010			15		4780	*
01			30		*	*
02			30		*	*
048	0.57	1100	30		4330	*
050			30		4430	*
053			60		*	*
054			60		*	*
011	0.59	1100	30		4430	*
012			30		4330	*
013			30		2480 x	-
014			30		2320 x	-
057			60		4020	*
058			60		4740	*
028			60		2480	*
030			60		*	*
097			90		4330	75.0
098			90		2080 x	-
095	120		3710 x	-		
096	120		*	*		

* No fracture at 5000 lb., equivalent to over 80 ksi.
 x Pre-existing crack, as shown by discolored part of fracture surface.

TABLE XII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 70 F HEAT TREATED AT 1150 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS wt/rd ² ksi
		°F	Minutes	App. Crack	Fracture	
07	0.51	1150	3		*	*
08			3		*	*
081	0.53	1150	3		*	*
082			3		*	*
015	0.55	1150	5		2890	*
03			5		2660	*
04			10		*	*
088	0.57	1150	10		4330	*
090			10		*	*
017			20		*	*
018			20		3710	*
069			30		2660 x	-
070			30		*	*
079			30		2320 x	-
080			30		2670 x	-
071	0.59	1150	30		4130	80.6
072			30		*	*
055			30		2660 x	-
056			30		2660 x	-

* No fracture at 5000 lb., equivalent to over 80 ksi.
 x Pre-existing crack, as shown by discolored part of fracture surface.

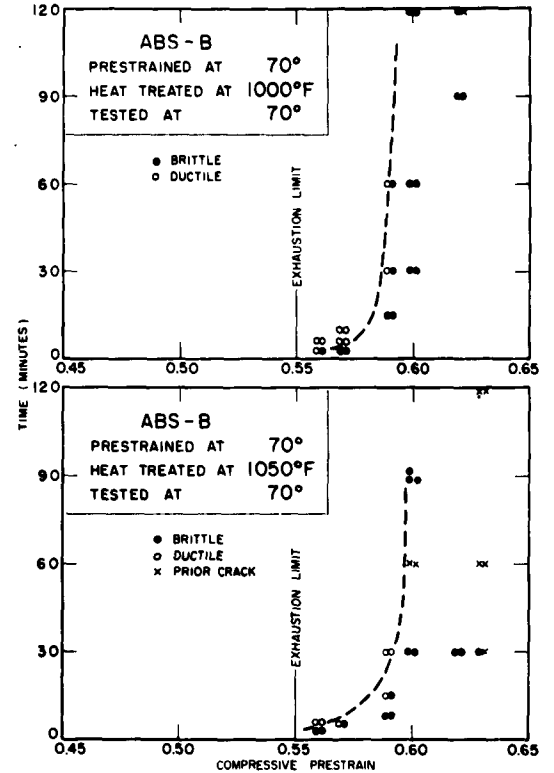


FIG. 6. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 70 F. HEAT TREATMENT AT 1000 & 1050 F; TESTS AT 70 F.

interesting though not altogether unexpected result is the restoration of ductility of hot strained bars at temperatures as low as 700°F. As shown in Figure 13 and Table XVII, bars prestrained a little above the exhaustion limit and heat treated at 750°F and 700°F for periods of 1 or 2 hours, may be ductile at -16°F. Likewise heat treatment at 750°F for 1-2 hours restores ductility at 70°F to bars strained just over the exhaustion limit at 550°F (Table XIII). Some ductility is very likely restored even in shorter heating periods, or at slightly lower temperatures, though not sufficient to enable the bars to withstand the full straining caused by a 5000 lb. load. An explanation may then be offered for the existence of a "worst"

TABLE XIII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F; HEAT TREATED AT 750 & 800 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS ksi
		°F	Minutes	App. Crack	Fracture	
B-322 B-323 B-320 B-321	0.37	750	60 120 120	- - -	3000 2880 4020 +	80.0 55.4 85.2 +
B-242 B-243 B-240 B-241 B-276 B-277 B-330 B-331	0.37	800	5 5 10 10 20 30 30	1230 - - - - - -	1440 1850 3090 2470 2060 + +	- 42.2 57.8 69.0 56.2 + +
B-290 B-291 B-294 B-295 B-296 B-297 B-326 B-327	0.40	800	20 40 40 80 120 120	- - - 600 - -	1850 2470 3300 3920 2480 + +	43.5 57.8 80.0 94.0 + +
B-292 B-293 B-298 B-299 B-302 B-303	0.43	800	40 40 60 120 120	- - - - -	3090 2680 1650 3300 4330 3920	74.3 62.1 + + + +

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XIV. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F; HEAT TREATED AT 850 & 900 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS ksi
		°F	Minutes	App. Crack	Fracture	
B-254 B-255 B-256 B-257 B-258	0.37	850	5 5 10 20 20	- 1130 - - -	1440 1850 3300 3300 +	39.0 - 73.5 67.7 +
B-260 B-261 B-266 B-267 B-327	0.40	850	20 20 40 40 60	- - - - -	3300 1600 2270 + +	76.0 94.8 74.2 + +
B-300 B-301 B-332 B-333 B-304 B-305	0.43	850	40 40 40 120 120	- 1440 - - -	2700 1850 3670 2060 +	64.0 - 74.0 64.3 +
B-314 B-315	0.45	850	120 120	- -	3020 4000	77.2 77.6
B-248 B-249 B-299	0.37	900	5 5 10	- - -	3100 + +	78.2 + +
B-262 B-263 B-267	0.40	900	5 5 10	- - -	2260 2450 +	41.7 + +
B-268 B-269 B-270 B-271 B-272	0.42	900	10 10 20 20 40	- - - - -	1440 1850 3090 2470 2060	63.7 63.6 63.2 61.6 26.11
B-276 B-277 B-310 B-311	0.43	900	5 5 10 120	1130 - 1200 -	1440 1850 3090 2470	39.0 - 73.5 67.7

* No fracture at 5000 lb., equivalent to over 80 ksi

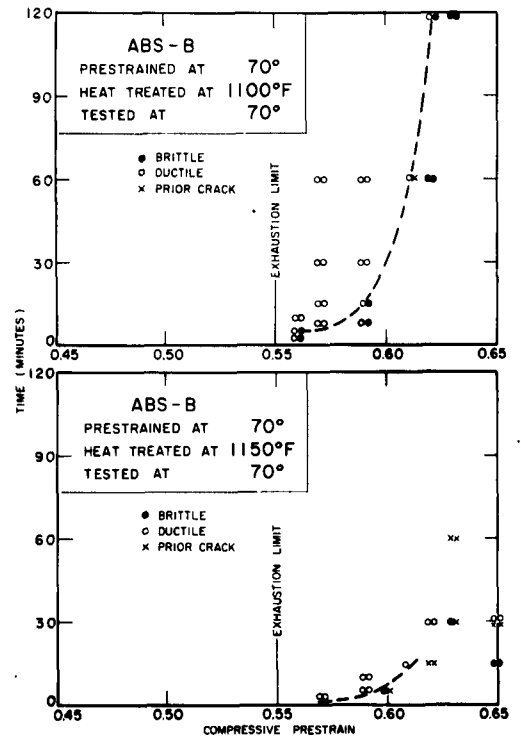


FIG. 7. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 70 F. HEAT TREATMENT AT 1100 & 1150 F; TESTS AT 70 F.

temperature around 550°F at which the exhaustion limit is least, and for the rapid increase of exhaustion limit as the prestraining temperature is raised above 600°F (Figures 4 and 5). The strain hardening, aging, and embrittlement appear to increase with the temperature, at least up to a point. Simultaneously a recovery or restoration of ductility appears to occur above a certain temperature and to become faster as the

TABLE XV. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 950 & 1000; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS	
		°F	Minutes	App. Crack	Fracture	lb/nd ²	ksi
B-200 B-201 B-204	0.37	950	3	-	+	+	+
B-206 B-207 B-215	0.40	950	3	-	3510	78.4	+
B-210 B-211 B-214 B-215 B-216 B-217 B-218 B-219	0.43	950	5	-	+	+	+
B-220 B-221 B-222 B-223 B-224 B-225 B-226 B-227 B-228 B-229	0.46	950	10	-	1850	44.2	+
B-230 B-231 B-232 B-233 B-234 B-235 B-236 B-237 B-238 B-239	0.48	950	20	-	3510	+	+
B-240 B-241 B-242 B-243 B-244 B-245 B-246 B-247 B-248 B-249	0.50	950	20	-	3920	85.2	+
B-250 B-251 B-252 B-253 B-254 B-255 B-256 B-257 B-258 B-259	0.52	1000	3	-	+	+	+
B-260 B-261 B-262 B-263 B-264 B-265 B-266 B-267 B-268 B-269	0.40	1000	5	-	1050	26.0	+
B-270 B-271 B-272 B-273 B-274 B-275 B-276 B-277 B-278 B-279	0.43	1000	10	-	+	+	+
B-280 B-281 B-282 B-283 B-284 B-285 B-286 B-287 B-288 B-289	0.46	1000	10	-	4330	69.7	+
B-290 B-291 B-292 B-293 B-294 B-295 B-296 B-297 B-298 B-299	0.50	1000	20	-	2880	70.0	+
B-300 B-301 B-302 B-303 B-304 B-305 B-306 B-307 B-308 B-309	0.40	1000	30	-	2680	65.6	+
B-310 B-311 B-312 B-313 B-314 B-315 B-316 B-317 B-318 B-319	0.43	1000	40	1230	1440	+	+
B-320 B-321 B-322 B-323 B-324 B-325 B-326 B-327 B-328 B-329	0.46	1000	60	820	1030	+	+

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XVI. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 1050 F; TESTED AT 70 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS	
		°F	Minutes	App. Crack	Fracture	lb/nd ²	ksi
B-210 B-217	0.37	1050	3	-	+	+	+
B-200 B-201	0.40	1050	3	-	+	+	+
B-206 B-207	0.43	1050	3	-	+	+	+
B-208 B-209	0.46	1050	3	-	1650	39.6	+
B-222 B-223 B-210 B-211	0.48	1050	5	-	3300	78.9	+
B-236 B-237 B-204 B-205	0.50	1050	5	-	1850	45.7	+
B-228 B-229 B-220 B-221	0.52	1050	10	-	2580	62.7	+
B-342 B-343	0.53	1050	40	620	1640	+	+

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XVII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F; HEAT TREATED AT 700-800 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS	
		°F	Minutes	App. Crack	Fracture	lb/nd ²	ksi
B-305 B-306 B-307 B-308 B-309 B-310	0.24	700	30	-	4330	81.4	+
B-307 B-308 B-309 B-310	0.24	750	20	-	3920	74.7	+
B-315 B-316 B-317 B-318 B-319 B-320	0.27	750	30	-	4840	101.0	+
B-232 B-233 B-234 B-235	0.24	800	5	-	1850	38.3	+
B-242 B-243 B-217 B-218 B-315 B-316	0.27	800	10	-	1650	40.1	+
B-278 B-279 B-283 B-284 B-311 B-312 B-319 B-380	0.30	800	10	-	2470	61.1	+
B-287 B-288 B-323 B-324 B-325 B-326	0.33	800	20	-	3090	74.5	+

TABLE XVIII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 850 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS	
		°F	Minutes	App. Crack	Fracture	lb/nd ²	ksi
B-252 B-253 B-244 B-245 B-399 B-400	0.24	850	3	-	1400	31.7	+
B-290 B-291	0.27	850	10	-	3300	63.4	+
B-290 B-281 B-285 B-286	0.30	850	10	-	1190	27.2	+
B-289 B-325 B-326 B-357 B-358 B-401 B-402	0.33	850	20	-	3500	83.8	+
B-331 B-332 B-333 B-334 B-335 B-336 B-337 B-338	0.36	850	30	-	1440	32.1	+
B-329 B-330	0.39	850	60	-	2060	47.3	+

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XIX. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 900 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kM/bd ² ksi
		°F	Minutes	Arr. Crack	Fracture	
B-236 B-237	0.24	900	3	-	3500	71.2
B-238 B-239 B-240 B-241 B-247 B-248 B-277 B-278	0.27	900	3	-	2840	45.3
			3	-	2600	61.9
			5	-	3000	63.4
			10	-	2680	55.3
			10	-	+	+
			20	-	+	+
B-246 B-247 B-248 B-249 B-250 B-251 B-252	0.30	900	5	-	+	+
			15	-	4360	+
			15	-	2880	64.4
			60	-	+	+
			60	-	+	+
B-276 B-277 B-254 B-255 B-256 B-257 B-258 B-259 B-260 B-261 B-262 B-263 B-264	0.33	900	5	-	1440	+
			5	-	2370	+
			10	-	+	+
			10	-	3000	+
			20	-	+	+
			20	-	3090	65.5
			30	-	3710	83.9
			30	-	+	+
			60	-	+	+
			60	-	3920	81.1
			120	-	+	+
			120	-	+	+
B-337 B-338 B-301 B-302 B-341 B-342	0.36	400	20	-	2260	51.2
			20	-	3300	73.0
			60	-	1850	42.8
			60	-	1500	35.5
			120	-	+	+
			120	-	3710	83.0
B-335 B-336	0.39	400	60	-	3500	78.1
			60	-	2670	55.0

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XX. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 950 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kM/bd ² ksi
		°F	Minutes	Arr. Crack	Fracture	
B-228 B-229	0.24	950	3	-	4200	82.0
B-248 B-249 B-250 B-251	0.27	950	3	-	3710	70.7
			3	-	+	+
			5	-	+	+
B-262 B-263 B-264 B-265	0.30	950	5	-	2260	48.0
			10	-	+	+
			10	-	+	+
B-272 B-273	0.25	950	10	-	2370	+
			10	-	3090	+
B-339 B-400 B-401 B-402	0.36	950	20	-	2260	50.3
			20	-	2260	+
			30	2260	2890	+
			30	-	+	+
B-383 B-384	0.37	950	60	3920	4120	+
			60	-	+	+
B-414 B-275 B-281 B-282	0.40	950	20	-	2500	50.2
			20	-	1690	39.7
			40	-	+	+
			40	-	+	+
B-294 B-303 B-359 B-360 B-361 B-392	0.43	950	50	-	2780	61.7
			50	-	2850	67.8
			90	-	2680	63.0
			90	-	2680	63.3
			120	-	+	+
			120	-	+	+

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XXI. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 1000 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kM/bd ² ksi
		°F	Minutes	Arr. Crack	Fracture	
B-266 B-267	0.24	1000	3	-	+	+
B-270 B-271 B-214 B-215	0.27	1000	3	-	2680	+
			3	-	+	+
			5	-	+	+
			5	-	+	+
B-260 B-261	0.30	1000	5	-	+	+
			5	-	+	+
B-256 B-257 B-222 B-223	0.33	1000	5	-	2680	58.5
			10	-	+	+
			10	-	+	+
B-210 B-211	0.35	1000	20	-	3090	58.3
			20	-	+	+
B-381 B-382	0.39	1000	40	-	+	+
			40	-	+	+
B-291 B-292	0.40	1000	20	-	2890	+
			20	-	+	+
B-385 B-386 B-395 B-396	0.43	1000	60	-	4120	89.1
			60	-	+	+
			90	-	2470	59.5
			90	-	3300	76.6
B-397 B-398	0.46	1000	90	-	1440	35.1
			90	-	2680	65.4

* No fracture at 5000 lb., equivalent to over 80 ksi

TABLE XXII. RESTORATION OF DUCTILITY OF BARS OF ABS-B STEEL PRESTRAINED AT 550 F HEAT TREATED AT 1050 F; TESTED AT -16 F.

BAR	PRE-STRAIN	HEAT TREATMENT		TEST LOAD (lb)		FRACTURE STRESS kM/bd ² ksi
		°F	Minutes	Arr. Crack	Fracture	
B-200 B-201	0.24	1050	3	-	+	+
			3	-	+	+
B-204 B-205	0.27	1050	3	-	+	+
			3	-	+	+
B-203 B-204	0.30	1050	3	-	+	+
			3	-	+	+
B-258 B-259 B-218 B-219	0.32	1050	3	-	1690	+
			3	-	+	+
			5	-	+	+
			5	-	+	+
B-220 B-221 B-206 B-227	0.35	1050	10	-	3500	75.8
			10	-	4300	83.0
			20	-	+	+
			20	-	3990	67.7
B-224 B-225 B-403 B-404	0.40	1050	20	-	+	+
			20	-	3710	83.1
			40	-	3190	70.9
			60	-	+	+
B-405 B-406	0.43	1050	90	-	+	+
			90	-	+	+
B-264 B-265	0.44	1050	20	-	3510	75.1
			20	-	3920	83.0

* No fracture at 5000 lb., equivalent to over 80 ksi

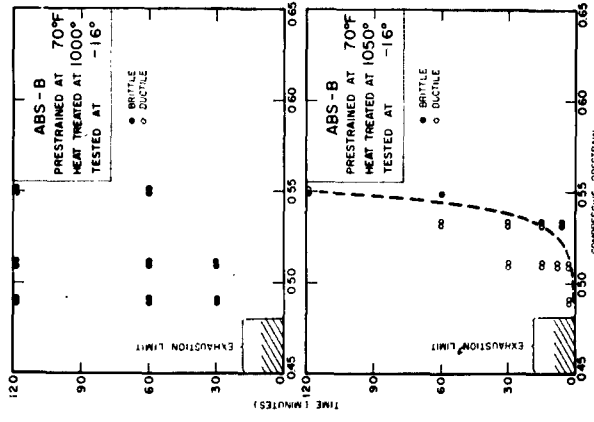


FIG. 8. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 70 F HEAT TREATMENT AT 1000 & 1050 F; TESTS AT -16 F.

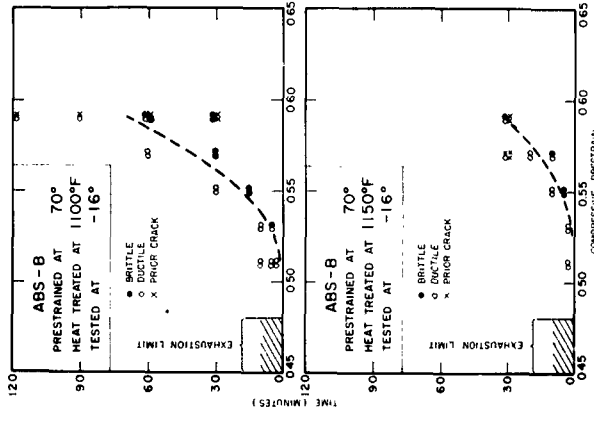


FIG. 9. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 70 F HEAT TREATMENT AT 1100 & 1150 F; TESTS AT -16 F.

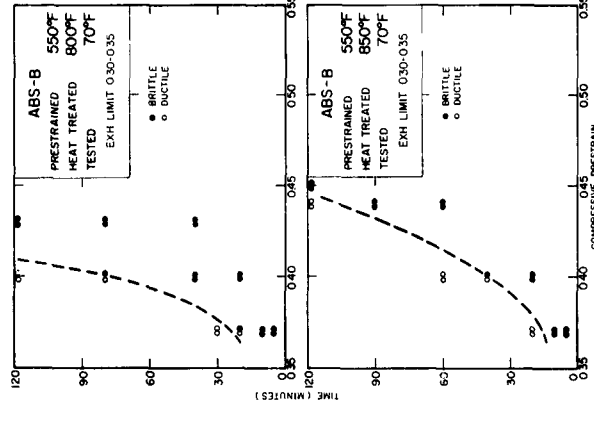


FIG. 10. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 800 & 70 F; TESTS AT 70 F.

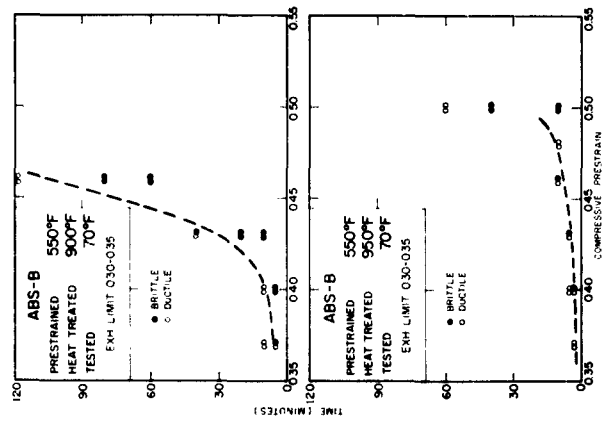


FIG. 11. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 900 & 950 F; TESTS AT 70 F.

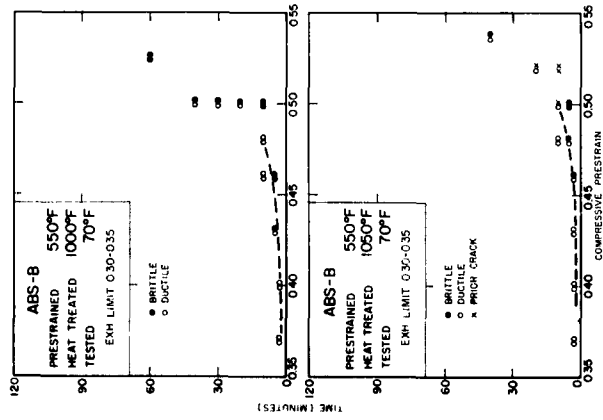


FIG. 12. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 1000 & 1050 F; TESTS AT 70 F.

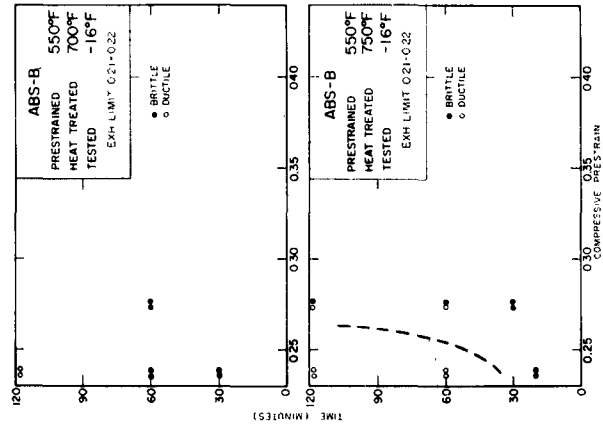


FIG. 13. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 700 & 750 F; TESTS AT -16 F.

temperature rises. The final behavior of the steel should be governed by the net effect of the two counteracting influences. Under the present test conditions the two influences cause the worse embrittlement at about 550°F. Above this temperature the rate of recovery is stronger and restores more ductility than is exhausted. A gain of restoration over exhaustion of a few per cent for every 50°F, is sufficient to produce the shape of the curves of Figures 4 and 5.

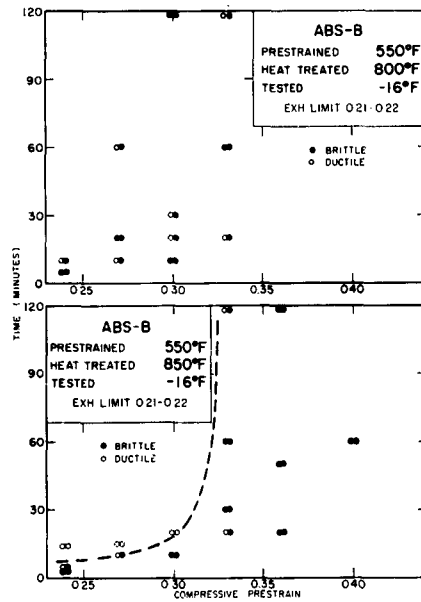


FIG. 14. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 800 & 850 F; TESTS AT -16 F.

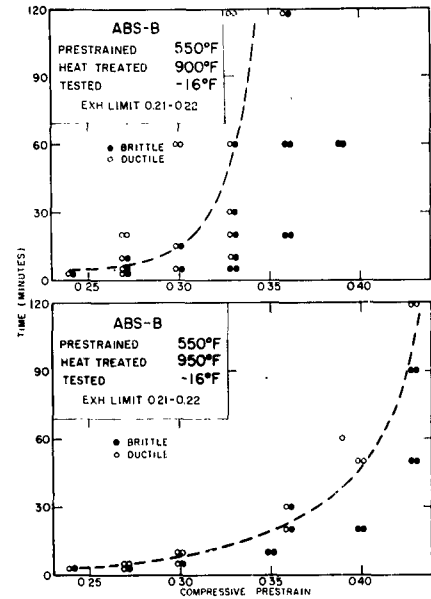


FIG. 15. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 900 & 950 F; TESTS AT -16 F.

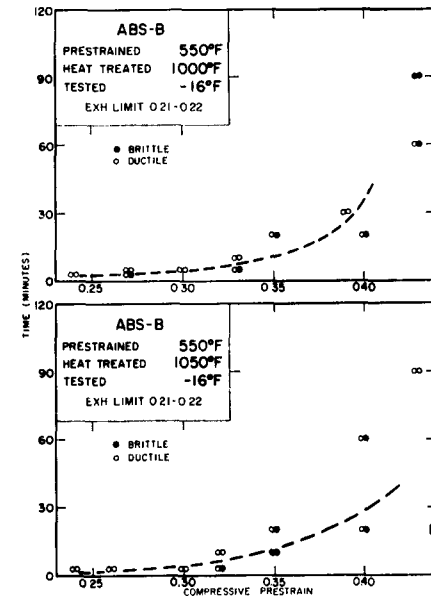


FIG. 16. RESTORATION OF DUCTILITY AFTER PRESTRAIN AT 550 F HEAT TREATMENT AT 1000 & 1050 F; TESTS AT -16 F.

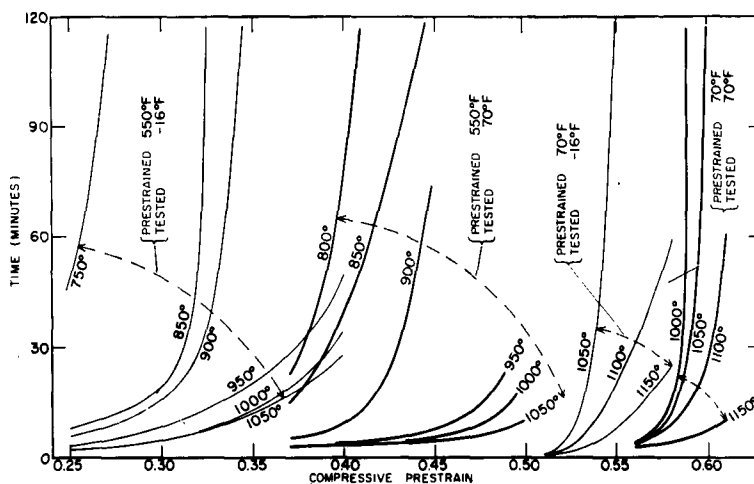


FIG. 17. APPROXIMATE CURVES OF MIN. HEAT TREATING TIME VS. PRESTRAIN FOR ABS-B STEEL BARS PRESTRAINED AT 70 AND 550 F AND TESTED AT 70 AND -16 F.

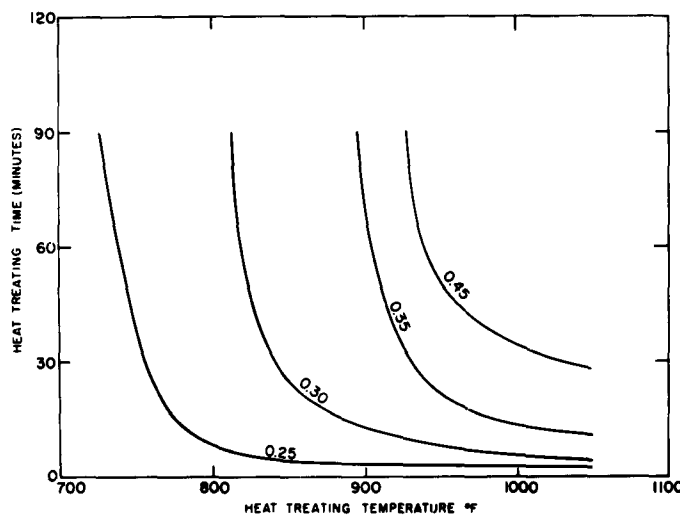


FIG. 18. APPROXIMATE CURVES OF MINIMUM HEAT TREATING TIME VS. TEMPERATURE FOR ABS-B STEEL BARS PRE-STRAINED BY CONSTANT AMOUNTS AT 550 F AND TESTED AT -16 F.

4. CONCLUSIONS

It has been found that ABS-B steel, like other steels studied in the past, suffers a sudden reduction of the extensional ductility at a narrowly determined limit of compressive prestrain. The exhaustion limit was determined for prestraining at 70° and -16° F. A "worst"

prestraining temperature was again found at about 550° F, where the exhaustion limit was about half as high as at 70° F.

Heat treatment at temperatures above 1000° F of bars embrittled by cold straining was found to restore sufficient ductility to permit extensional strains of over 0.10 (10%) without fracture. The required duration of heating was found

to increase very rapidly with the amount of prestrain, so that at each of the tested temperatures a practical cut-off prestrain existed, beyond which impractically long heating times appeared to be needed. The required heat treating time decreased rapidly as the temperature was raised.

Restoration of ductility was much faster and could be achieved at considerably lower temperatures in bars which had been embrittled by prestraining at 550°F than at 70°F. Bars prestrained little beyond the exhaustion limit at 550°F could be made ductile in two hours even at 700°F. It appears that the process of restoration of ductility takes place continuously and gradually during heat treatment, and that some restoration of ductility may occur even in short heating cycles and at lower temperatures than 700°F. The "worst" prestraining temperature would then appear to result from the most unfavorable net effect of two opposite tendencies, namely the embrittlement by straining and aging, and the rate of recovery, both of which appear to increase with temperature.

It may be concluded that suitable heat treatment can restore sufficient ductility to prevent brittle failures, but requires a specified time which depends not only on the temperature but also quite strongly on the type and amount of prestrain embrittlement. The experimentally determined time-temperature-prestrain curves with ABS-B steel indicate the following trends:

- A. Restoration of ductility is easier in hot than in cold strained bars.
- B. Some restoration of ductility appears to occur even at 700°, and maybe even less, for hot strained bars.
- C. The required heating time increases with the amount of prestrain, and becomes impractically long beyond a certain limiting prestrain.
- D. An increase of temperature reduces the required heating time and increases the limiting prestrain.
- E. Heating for about 1/2 to 1 hour at 1050°F or more would seem necessary for bars strained hot, and at 1150°F or more for bars strained cold. It is not known, however, if these heat treatments are sufficient for the most severe prestrains.

REFERENCES

1. Wells, A. A., "The Mechanics of Notch Brittle Fracture," *Welding Research*, 7, 34-r to 56-r (1953).
2. Wells, A. A., "The Influence of Welding on Notch Brittle Fracture," *J. West. of Scot. Iron Steel Inst.*, 60, 313-325 (1953)
3. Drucker, D. C., "An Evaluation of Current Knowledge of the Mechanics of Brittle Fracture," *Ship Structure Committee Report SSC-69* (1954).
4. Mylonas, C., Drucker, D. C., and Isberg, L., "Brittle Fracture Initiation Research Supplement, pp. 9-s to 17-s (1957)
5. Mylonas, C., Drucker, D. C., and Brunton, J. D., "Static Brittle Fracture Initiation at Net Stress 40% of Yield," Nobs-65917/3. *The Welding Journal*, Vol. 37, No. 10, Research Supplement, pp. 473-s to 479-s, (1958).
6. Mylonas, C., "Prestrain, Size and Residual Stresses in Static Brittle Fracture Initiation," Nobs-65917/4, *The Welding Journal*, Vol. 38, No. 10, Research Supplement, pp. 414-s to 424-s (1959).
7. Drucker, D. C., Mylonas, C., and Lianis, G., "On the Exhaustion of Ductility of E-Steel in Tension Following Compressive Prestrain," Nobs-65917/5, *The Welding Journal*, Vol. 39, No. 3, Research Supplement, pp. 117-s to 120-s (1960).
8. Mylonas, C., "Exhaustion of Ductility as a Fundamental Condition in Static Brittle Fracture Initiation," Nobs-65917/6. Published in "Brittle Fracture in Steel," Proc. of a Conference sponsored by the Brit. Admiralty Advisory Committee on Structural Steel in Cambridge, England 28-30 Sept. 1959. H. M. Stat. Office 1962, p. 167-173.
9. Ludley, J. H., and Drucker, D. C., "Size Effect in Brittle Fracture of Notched Steel Plates in Tension," *App. Mech.* 28 (1961) 137.
10. Ludley, J. H., and Drucker, D. C., "A Reversed-Bend Test to Study Ductile to Brittle Transition," Nobs-78440/3, *The Welding Journal*, Vol. 39, No. 12, Research Supplement (1959).
11. Rockey, K. C., Ludley, J. H., and Mylonas, C., "Exhaustion of Extensional Ductility Determined by Reversed Bending of 5 Steels," Nobs-78440/5, March 1961. *Proc. ASTM*, Vol. 62 (1962) 1120-1133.
12. Mylonas, C., and Rockey, K. C., "Exhaustion of Ductility by Hot Extension. An Explanation of Fracture Initiation Close to Welds," Nobs-78440/6 of the Division of Engineering, Brown University, March 1961; published under the title, "Exhaustion of Ductility by Hot Straining. An Explanation of Fracture Initiation Close to Welds," *The Welding Journal*, Vol. 40(7) Research Supplement, p. 306-s to 310-s, July 1961.
13. Mylonas, C., "Static Brittle Fracture Initiation Without Residual Stresses," Report Nobs-78440/4, *Welding Journal*, Vol. 40, No. 11, Research Supplement (1961)
14. Drucker, D. C., "A Continuum Approach to the Fracture of Solids." Chapter I in "Brittle Fracture" (D. C. Drucker and J. J. Gilman, Editors) Interscience, 1963.
15. Mylonas, C., "Exhaustion of Ductility and Brittle Fracture of Project E-Steel Caused by Prestrain and Aging", Report Nobs-88294/1 of the Division of Engineering, Brown University, Dec. 1963.

16. Turner, C. E., "A Note on Brittle Fracture Initiation in Mild Steel by Prior Compressive Prestrain," *Journal Iron & Steel Inst.*, Vol. 197, No. 2, pp. 131-135 (1961).
17. Shank, M. E. "Brittle Failure in Carbon Steel Structures other than Ships", *Welding Res. Council, Bulletin No. 17*, Jan. 1954.
18. Shank, M. E. "The Control of Steel Construction to Avoid Brittle Fracture," Published by Welding Research Council, New York. (1957).
19. Greene, T. W., "Evaluation of Effect of Residual Stresses," *The Welding Journal*. 28 (5) Res. Supplement, 193-s to 204-s (1949).
20. Wells, A. A. "The Brittle Fracture Strength of Welded Steel Plates," *Proc. Inst. Nav. Architects*, 1956.
21. DeGarmo, E. P. "Preheat vs. Low- and High-Temperature Stress Relief Treatments," *The Welding Journal*, 31 (5), Research Supplement, 233-s to 237-s (1952).
22. Weck, R., "Experiments on Brittle Fracture of Steel Resulting from Residual Welding Stresses," *Welding Research*, 6, 70-r to 82-r. (1952).
23. Kennedy, R., "The Influence of Stress-Relieving on the Initiation of Brittle Fracture in Welded Plate Specimens," *Brit. Welding Jnl.*, 4 (11), 529-534 (November 1957).
24. Kihara, H., and Masubuchi, V., "Effect of Residual Stress on Brittle Fracture." *The Welding Journal*, 37 (4), Research Suppl., 157-s to 168-s (1959).
25. Wells, A. A. "Influence of Residual Stresses and Metallurgical Changes on Low Stress Brittle Fracture in Welded Steel Plates," *Welding Journal* 40 (4), Research Suppl. (1961) 182-s.
26. Wells, A. A. and Burdekin, F. M. "Effects of Thermal Stress Relief and Stress Relieving Conditions on the Fracture of Notched and Welded Wide Plates," Report B6/23/62 of the British Welding Research Association (Oct. 1962) reprinted in *Welding Research Abroad*, IX, No. 7 (Aug. Sept. 1963) 24-30.
27. Hebrant, F., Louis, H., Soete, W., and Vinckier, A., "Resultats de quelques Essais de Rupture Fragile Consideres du Point de Vue du Constructeur" *Revue de la Soudure* 13 No. 1 (1957) 31-48. Also 11 No. 3 (1955).
Soete, W. "Contribution a l'Etude du Probleme des Ruptures Fragiles" *Revue de Metallurgie LIV* No. 1 (Jan. 1957). 71-79.
28. Hall, W. T., Nordell, W. T., and Munse, W. H. "Studies of Welding Procedures" *The Welding Journal*, 41 (11), Research Supplement, Nov. 1962).
29. Videon, F. F., Barton, F. W. and Hall, W. J., "Brittle Fracture Propagation Studies," *Ship Structure Committee Report SSC-148* (1963).
30. Soete, W., "Aspects Mechaniques de la Rupture Fragile des Aciers." *Houdremont Lecture of IIW*, 1959. *Revue de la Soudure*. Vol. 16, No. 2, Brussels, June 1960, 165-194.
31. Osgood, W. R., Editor *Residual Stresses in Metals and Metal Construction*. Rheinhold, New York, 1954.
32. Boyd, G. M., "Metallurgical Concomitants of Residual Stress". Document IX-260-60 presented at the Intern. Inst. of Welding, 1960.
33. Forster, S., Rauterkus, W., Thielman, H., and Thyssen F., "Über die Alterungs-bestandigkeit von Blechschweißungen", *Schweissen u. Schneiden* 9 (1957) 447-57.

34. Hatch, W. P., Travis, K. E., and Hartbower, C. E., "Welding Low Carbon Martensite", *Welding Journal* 39 (4), Research Suppl., April 1960. 141-s to 146-s.
35. Dekker, P. F. W. "Some experiments on the Metallurgical Concomitants of Residual Stress", Doc. of Commission ix of Int. Inst. of Welding. 1962.
36. Korber, F., Eichinger, A., and Moller, H., "Verhalten Gestauchter Metalle bei Zugbeanspruchung," Kaiser-Wilhelm Institut f. Eisenforschung, part I, 23 (1941), 123-33; part II, 26 (1943), 71-89.
37. Osborn, C. J., Scotchbrook, A. F., Stout, R. D., and Johnston, B. G., "Effect of Plastic Strain and Heat Treatment," *Welding Journal*, 28 (8), Research Supplement, 337-s to 353-s, (1949).
38. Ripling, E. J., and Sachs, G. "The Effect of Strain-Temperature History on the Flow and Fracture Characteristics of Annealed Steel", *Trans. Am. Inst. Min. Met. Eng.* 185 (1949) 78.
39. Polakowski, N. H., "Softening of Metals during Cold Work", *J. Iron Steel Inst.* 169 (1951) 337-46.
40. Polakowski, N. H., "Restoration of Ductility of Cold Worked Aluminum, Copper, and Low Carbon Steel by Mechanical Treatment", *Proc. ASTU* 52 (1952) 1086-97.
41. MacCutcheon, E. M., Jr., and Wright, Willard A., "Transition Characteristics of Prestrained Notched Steel Specimens in Tension", *David Taylor Model Basin, Report* 767, January 1952.
42. Ripling, E. J., and Baldwin, W. M., Jr., "Overcoming Rheotropic Brittleness: Precompression vs. Pre-tension." *ASM Trans.*, 44, (1952), 1047.
43. Lankford, W. T., "Effect of Cold Work on the Mechanical Properties of Pressure Vessel Steels", *The Welding Journal*, 35 (4), Research Supplement, 195-s to 206-s (1956).
44. Parker, E. R., "Brittle Fracture of Engineering Structures", Wiley, New York, (1957).
45. Lagasse, P. E., and Hofmans, M., "L'aptitude des aciers au profilage a froid", report CNRM F/c/7-RA6, Nov. 1958.
46. Lagasse, P. E., and Hofmans, M., "Effets thermiques sur la fragilite des aciers doux," report ANRM F/c/7-RA101, Aug. 1959.
47. Lagasse, P. E. "Sur la Fragilisation des Aciers Doux par Formage a Froid", report ANRM RA-198/62, July 1962. Liege, Belgium.
48. Allen, N. P., "The Mechanical Properties of the Ferrite Crystal", Eleventh Hatfield Memorial Lecture. *Journal Iron & Steel Inst.*, Vol. 191, Part I, pp. 1-18, Jan. 1959.
49. Rendall, J. H., Discussion in "Brittle Fracture in Steel", proceedings of a Conference sponsored by the British Admiralty Adv. Committee on Struct. Steel, Cambridge Sept. 1959, HM Stat. Office 1962, p. 103. Also private communication.
50. Tipper, C. F., "The Brittle Fracture Story", Cambridge Univ. Press, 1962.
51. Terazawa, K., Otani, M., Yoshida, T., and Terai, K., "Effect of High Temperature Prestraining on Notch Toughness of Steel", Report of Kawasaki Dockyard Co., Kobe, Japan (Jan. 1961). Presented as document IX-285-61 at the annual meeting of the Inter. Inst. of Welding, New York (April 1961).

52. Terazawa, K., Otani, M., Yoshida, T., and Terai, K., "Effect of High Temperature Prestraining on Retained Ductility of Steel." Report of Kawasaki Dockyard Co., Kobe, Japan (Jan. 1961). Presented as document IX-285-61 at the annual meeting of the Inter. Inst. of Welding, New York (April 1961).
53. Yao, J. T. P., and Munse, W. H., "Low Cycle Fatigue Behavior of Axially loaded Specimens of Mild Steel", Report No. SSC-151 of the Ship Structure Committee, June 1963.
54. Srawley, J. E., and Beachem, C. D., "Crack Propagation Tests of High Strength Sheet Materials, Part IV-The Effect of Warm Prestraining" NRL Report 5460, April 1960.
55. Brothers, A. J., and Yukowa, S. "The Effect of Warm Prestraining on Notch Fracture Strength" Paper 62-Met-1 of the ASME presented at a joint AWS-ASME Conference, April 1962.
56. Pense, A. W., Stout, R. D., and Kottcamp E. H., Jr., "A Study of Subcritical Embrittlement in Pressure Vessel Steels", The Welding Journal 28 (12), Res. Suppl. (1963) 541-s to 546-s.

NONE

Security Classification

DOCUMENT CONTROL DATA - R&D		
<i>(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)</i>		
1. ORIGINATING ACTIVITY (Corporate author)	2. REPORT SECURITY CLASSIFICATION	
Ship Structure Committee	NONE	
	2b. GROUP	
3. REPORT TITLE		
RESTORATION OF DUCTILITY OF HOT OR COLD STRAINED ABS-B STEEL BY HEAT TREATMENT AT 700 to 1150 F		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)		
Progress Report		
5. AUTHOR(S) (Last name, first name, initial)		
Mylonas, C. and Beaulieu, R. J		
6. REPORT DATE	7a. TOTAL NO. OF PAGES	7b. NO. OF REFS
April 1965	22	56
8a. CONTRACT OR GRANT NO.	8c. ORIGINATOR'S REPORT NUMBER(S)	
NObs-88294	NObs-88294/2	
b. PROJECT NO.		
c.	8b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
Serial No. S-F 013-02-04 Task 2022		
d.		
10. AVAILABILITY/LIMITATION NOTICES		
All distribution of this report is controlled. Qualified DDC users shall request through Ship Structure Committee, U. S. Coast Guard Headquarters, Washington, D. C.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY	
	Bureau of Ships, Dept. of the Navy Washington, D. C	
13. ABSTRACT		
<p>The severe embrittlement caused by a suitable history of strain and temperature has been confirmed also for steel conforming to ABS-B classification. Steel prestrained in compression by about 50% at 70°F and subsequently tested in tension fractures at an extensional strain of the order of 1%. Prestraining at 550°F by even 25% cause brittleness in extension at -16°F. Local severe embrittlement of this nature has been shown to be the basic cause of the static initiation of brittle failure of structures at low average stress. This is confirmed by service failures, whose origin is frequently traced to cold worked areas, or to the hot strained regions of defects close to welds.</p> <p>It is shown that a suitable heat treatment can restore appreciable ductility to steel embrittled by hot or cold straining. The duration of heating decreases with the temperature, but increases very rapidly with the amount of prestrain. To each temperature corresponds a limiting prestrain for which heat treatment becomes impractically long. Cold strained steel requires considerably longer heat treatment and higher temperatures (1000-1200°F) than hot strained steel (700-1000°F). Approximate time-temperature-prestrain curves have been experimentally determined.</p> <p>The results confirm that a major beneficial effect of the so-called "Thermal stress-relieving" treatment is a restoration of the ductility of locally embrittled steel.</p>		

DD FORM 1473
1 JAN 64

NONE
Security Classification

NONE
Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (corporate author) issuing the report.
- 2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.
- 2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.
3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.
4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.
5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.
6. **REPORT DATE:** Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.
- 7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.
- 7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.
- 8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.
- 8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.
- 9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.
- 9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).
10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, roles, and weights is optional.

DD FORM 1473 (BACK)
1 JAN 64

NONE

Security Classification

NATIONAL ACADEMY OF SCIENCES-NATIONAL RESEARCH COUNCIL
DIVISION OF ENGINEERING AND INDUSTRIAL RESEARCH

The Ship Hull Research Committee undertakes research service activities in the general fields of materials, design, and fabrication, as relating to improved ship hull structure, when such activities are accepted by the Academy as part of its functions. The Committee recommends research objectives and projects; provides liaison and technical guidance to such studies; reviews project reports; and stimulates productive avenues of research.

SHIP HULL RESEARCH COMMITTEE

Chairman: RADM A. G. Mumma, USN (Ret.)
Executive Vice President
Worthington Corporation

Members: Prof. F. L. Couch, Chairman
Dept. of Naval Architecture
& Marine Engineering
University of Michigan

Professor J. E. Goldberg
Prof. of Civil Engineering
Purdue University

Mr. Hollinshead de Luce
Asst. to Vice President
Bethlehem Steel Co.

Mr. James Goodrich
Exec. Vice President
Bath Iron Works

Dr. C. O. Dohrenwend
Vice President & Provost
Rensselaer Polytechnic Inst.

Mr. D. C. MacMillan
President
George G. Sharp, Inc.

Prof. J. Harvey Evans
Prof. of Naval Architecture
Mass. Institute of Technology

Arthur R. Lytle
Director

R. W. Rumke
Executive Secretary

SR-158 PROJECT ADVISORY COMMITTEE
"Macrofracture Fundamentals"

Chairman: Professor W. R. Osgood
Professor of Civil Engineering
Catholic University of America

Members: Professor Joseph Kampner
Professor & Director of
Applied Mechanics
Polytechnic Institute of Brooklyn

Professor P. M. Naghdi
Professor of Engineering Science
University of California, Berkeley

Mr. J. A. Kies
Head, Ballistics Branch
Mechanics Division
Naval Research Laboratory

Dr. Nicolas Perrone
Structural Mechanics Branch
Office of Naval Research