

UNCLASSIFIED

AD NUMBER
AD463306
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative/Operational Use; 28 FEB 1965. Other requests shall be referred to Army Electronics Command, Fort Monmouth, NJ.
AUTHORITY
USAECON 1tr, 18 Apr 1977

THIS PAGE IS UNCLASSIFIED

UNCLASSIFIED

AD. 4 6 3 3 0 6

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

463306

CATALOGED BY: DDC

AS AD 17

**RESEARCH AND DEVELOPMENT PROGRAM
INTRINSIC RELIABILITY
SUBMINIATURE CERAMIC CAPACITORS**


ELEVENTH QUARTERLY PROGRESS REPORT

PERIOD: 1 DECEMBER 1964 - 28 FEBRUARY 1965

TO

**U. S. ARMY SIGNAL RESEARCH & DEVELOPMENT LABORATORY
FORT MONMOUTH, NEW JERSEY**

**CONTRACT NO. DA-36-039-SC-90705
D. A. PROJECT NO. 1P6 22001 A 057**

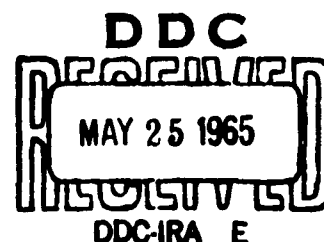

**SPRAGUE ELECTRIC COMPANY
NORTH ADAMS, MASSACHUSETTS**

4 6 3 3 0 6

**QUALIFIED REQUESTORS MAY OBTAIN COPIES OF THIS REPORT FROM
DEFENSE DOCUMENTATION CENTER, CAMERON STATION, ALEXANDRIA, VIRGINIA.
FOREIGN ANNOUNCEMENT AND DISSEMINATION OF THIS REPORT
BY D. D. C. IS NOT AUTHORIZED.**

RESEARCH AND DEVELOPMENT PROGRAM
INTRINSIC RELIABILITY
SUBMINIATURE CERAMIC CAPACITORS

Eleventh Quarterly Report

Period: 1 December 1964 - 28 February 1965

Object of Study: To conduct investigations leading to the approaches for the attainment of high reliability in subminiature ceramic capacitors and the determination of failure rate as a function of voltage and temperature.

Contract No. DA-36-039-SC-90705
D. A. Project No. 1P6 22001 A 057

Controlling Specifications:

Signal Corps Technical Guidelines, "Reliability Long Life
Component Studies," 3 November 1961

Signal Corps Technical Requirements No. SCL-2101N,
14 July 1961

Report Prepared by:

P. M. Kennedy
T. I. Prokopowicz

TABLE OF CONTENTS

	<u>Page</u>
SECTION 1 - PURPOSE	1-1
SECTION 2 - ABSTRACT	2-1
SECTION 3 - PUBLICATIONS, LECTURES, REPORTS, AND CONFERENCES	3-1
SECTION 4 - FACTUAL DATA	
4.1 Construction of C67 Case Size I MONOLYTHIC Capacitors	4-1
4.2 Selection of Long Life Capacitors of the Improved Version	4-1
4.3 Voltage-Temperature Matrix	4-3
4.4 Capacitors Having 1.5 Mil Dielectric Layers	4-5
SECTION 5 - CONCLUSIONS	5-1
SECTION 6 - PROGRAM FOR NEXT QUARTER	6-1
SECTION 7 - DISTRIBUTION LIST	7-1
SECTION 8 - IDENTIFICATION OF PERSONNEL	8-1

SECTION 1

PURPOSE

The purpose of this contract is to carry out research work involving investigations leading to approaches to the attainment of high reliability in subminiature ceramic capacitors and the determination of failure rate as a function of voltage and temperature.

In particular, this involves the following:

- (1) Construction of a model or theory to predict failure mechanisms and failure rates as a function of voltage and temperature.
- (2) Development and evaluation of a short-term test to eliminate early failures effectively without shortening the time to the wearout mode of failure.
- (3) A determination of the failure rate as a function of voltage and temperature through large-scale life testing. From the data thus obtained, derating curves will be derived and overall failure rates for operating conditions will be estimated. The theory developed will be critically examined and refinements made.
- (4) Compilation of quarterly progress reports in accordance with Signal Corps Technical Requirements No. SCL-2101N, dated 14 July 1961.
- (5) Compilation of a final report in accordance with Signal Corps Technical Requirements No. SCL-2101N, dated 14 July 1961.

SECTION 2

ABSTRACT

Testing of C67 Case Size I MONOLYTHIC® capacitors of the improved version continues to demonstrate the long-life capability of this capacitor at use conditions. The testing of 124 of these capacitors at 200 VDC and 125°C for 2500 hr without catastrophic failure, then at 400 VDC and 125°C for 4000 hr with only five displaying any degradation, continues to indicate the intrinsic high reliability of this unit.

Some properties of 1800 capacitors (0.01 μ f rating) manufactured for voltage-temperature matrix testing were examined.

The duration of the contract has been extended to permit statistical demonstration of the validity of the long life capacitor selection technique.

SECTION 3

PUBLICATIONS, LECTURES, REPORTS, AND CONFERENCES

The Tenth Quarterly Progress Report, covering the period September 1, 1964 - November 30, 1964, was submitted for U. S. Army Electronics Research and Development Agency approval.

SECTION 4

FACTUAL DATA

4.1 Construction of C67 Case Size I MONOLYTHIC Capacitors


The C67 Case Size I MONOLYTHIC capacitor has a construction of stacked ceramic dielectric layers 0.0025 in. thick and connected electrically in parallel. These layers are intimately bonded to each other through high-temperature sintering. The ceramic material is a barium titanate, which has a dielectric constant of about 2000 at room temperature and is stable to +10%, -15% between -55°C and +125°C. The capacitor is enclosed in a tubular case which is 0.25 in. long and has a diameter of 0.095 in.

4.2 Selection of Long Life Capacitors of the Improved Version

An experiment designed to establish a procedure for the selection of long life capacitors of the improved version was begun during the eighth quarter and is still in progress. An outline of the various parts of the experiment is presented in Figure 1. Basically, the plan was to demonstrate that life lost by a capacitor during a brief period of accelerated testing can be regained by application of direct voltage of opposite sense for some given time. Furthermore, it was planned to demonstrate that if a particular capacitor is capable of a given performance at some accelerated condition, it will deliver at least a certain minimum standard of performance at milder conditions. This latter objective was obtained during the ninth quarter and was reported in the Ninth Quarterly Progress Report.

Properties of the 124 C67 Case Size I MONOLYTHIC capacitors of the improved version chosen for the experiment were described in the Eighth Quarterly Progress Report. Of these 124 capacitors, 53 were subjected to a two-part screening procedure incorporated into the experiment outlined in Figure 1. The screening procedure comprised the following steps:

- Step 1 - The capacitors are subjected to 300 VDC at 150°C for 72 hr, during which time the resistance of acceptable capacitors may not vary more than 20%.

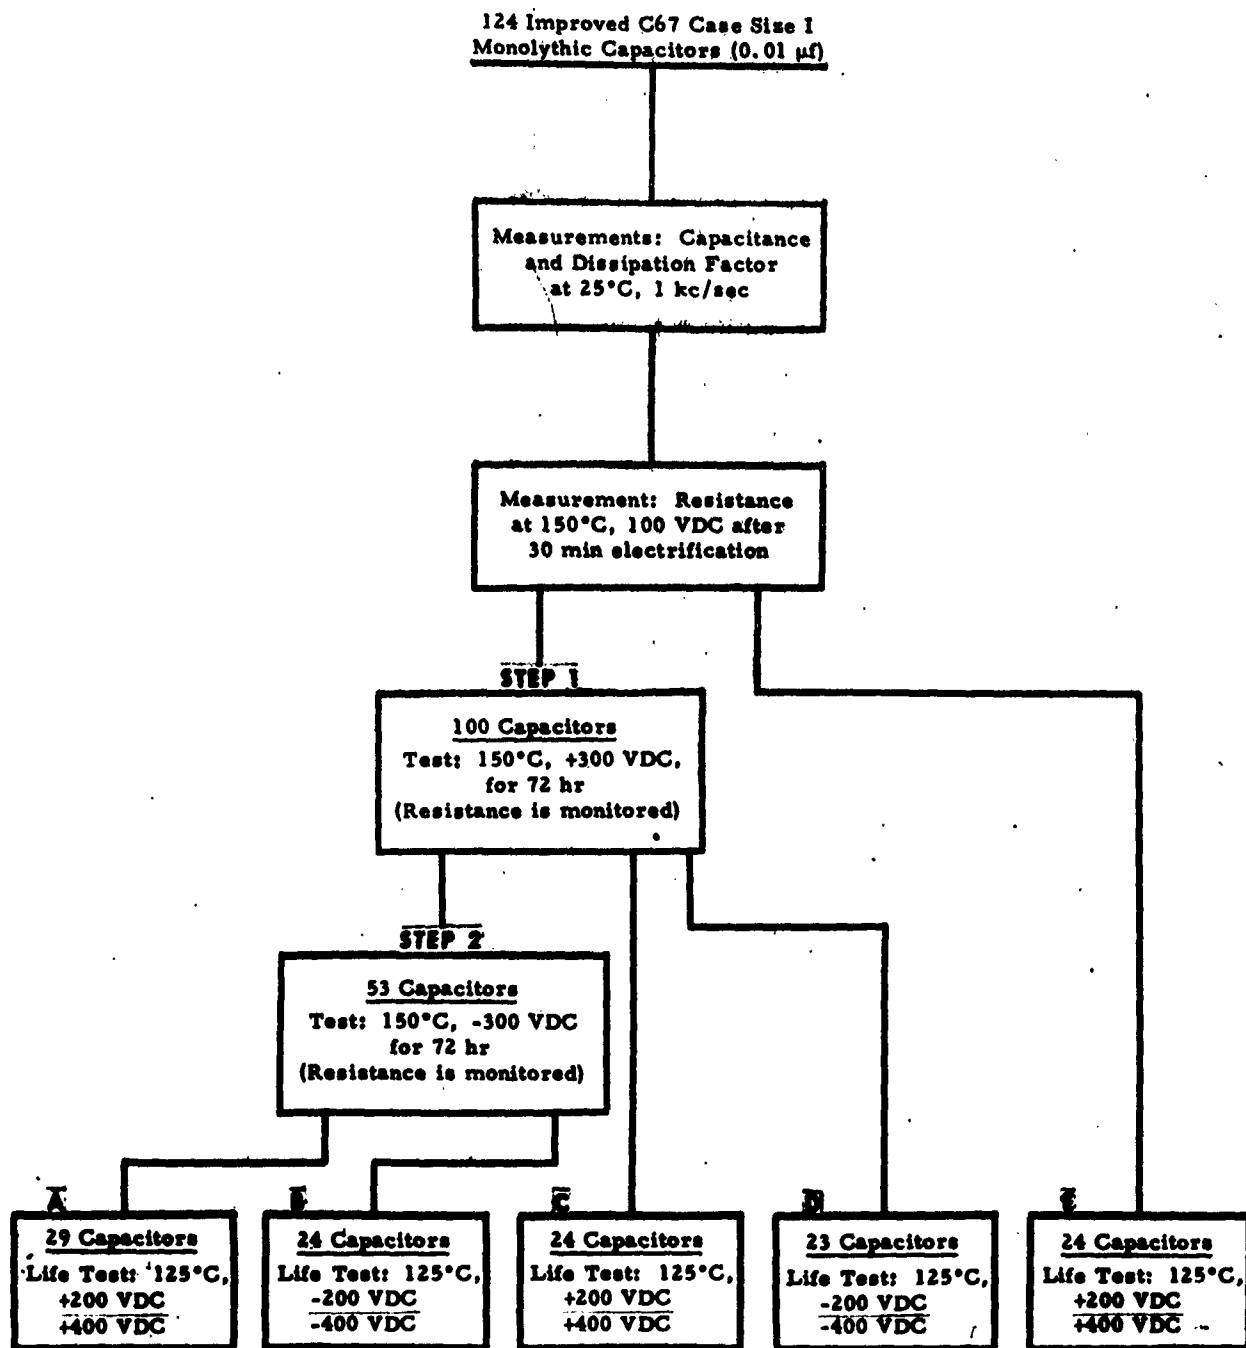

EXPERIMENT TO SELECT CAPACITORS HAVING POTENTIALLY LONG LIVES

Figure 1


Step 2 - The acceptable capacitors from Step 1 are subjected to 300 VDC, applied in the opposite sense at 150°C for 72 hr, during which time the resistance of acceptable capacitors may not vary more than 20%.

The purpose of Step 1 of the screening program is to identify those capacitors which have not reached the point of onset of degradation. The purpose of Step 2 is to rejuvenate normal capacitors and to detect those capacitors which are sensitive to voltage polarity because of a construction or material defect.

Life testing of the 124 capacitors was conducted at 125°C and 200 VDC for 2500 hr. None of the 53 capacitors which passed the screening procedure had reached the onset of degradation by the end of that time. (These capacitors are represented in Positions A and B of Figure 1.) Information regarding this life testing was published in the Ninth Quarterly Progress Report.

At the end of 2500 hr of testing at 125°C and 200 VDC, the life test voltage on the 124 capacitors was increased to 400 VDC. A total of 4000 hr of test time have been accumulated at this new condition. Two of the 53 capacitors which were subjected to both steps of the screening procedure are displaying marked degradation. Figure 2 shows resistance plotted as a function of time for several of the 53 capacitors. The two non-typical capacitors, Nos. 277 and 278, had initial RC products of 63 MΩ-μf and 200 MΩ-μf, respectively, at 150°C. This should be compared with the average RC product value of 130 MΩ-μf shown in Figure 18 of the Eighth Quarterly Progress Report. The relative resistances these two capacitors exhibited as a consequence of Step 1 in the screening procedure were 0.99 and 0.96, respectively. This should be compared with the average value of 0.94 shown in Figure 20 of the Eighth Quarterly Progress Report. The relative resistances these two non-typical capacitors exhibited as a consequence of Step 2 in the screening procedures were 0.90 and 0.88, respectively. This may be compared with the average value of 0.91 indicated in Figure 23 of the Eighth Quarterly Progress Report. It may be concluded that none of the measured values for Capacitor Nos. 277 and 278 before life test can be suspected to indicate the non-typical behavior noted for these capacitors during life test at 400 VDC, 125°C.


Resistance as a function of time for capacitors which were not subjected to either screening step is shown in Figure 3. These capacitors are represented in Position E in Figure 1. The general behavior of capacitors subjected to the screening procedure is similar to these. The slight decrease in resistance between 100 hr and 500 hr is due to a slight

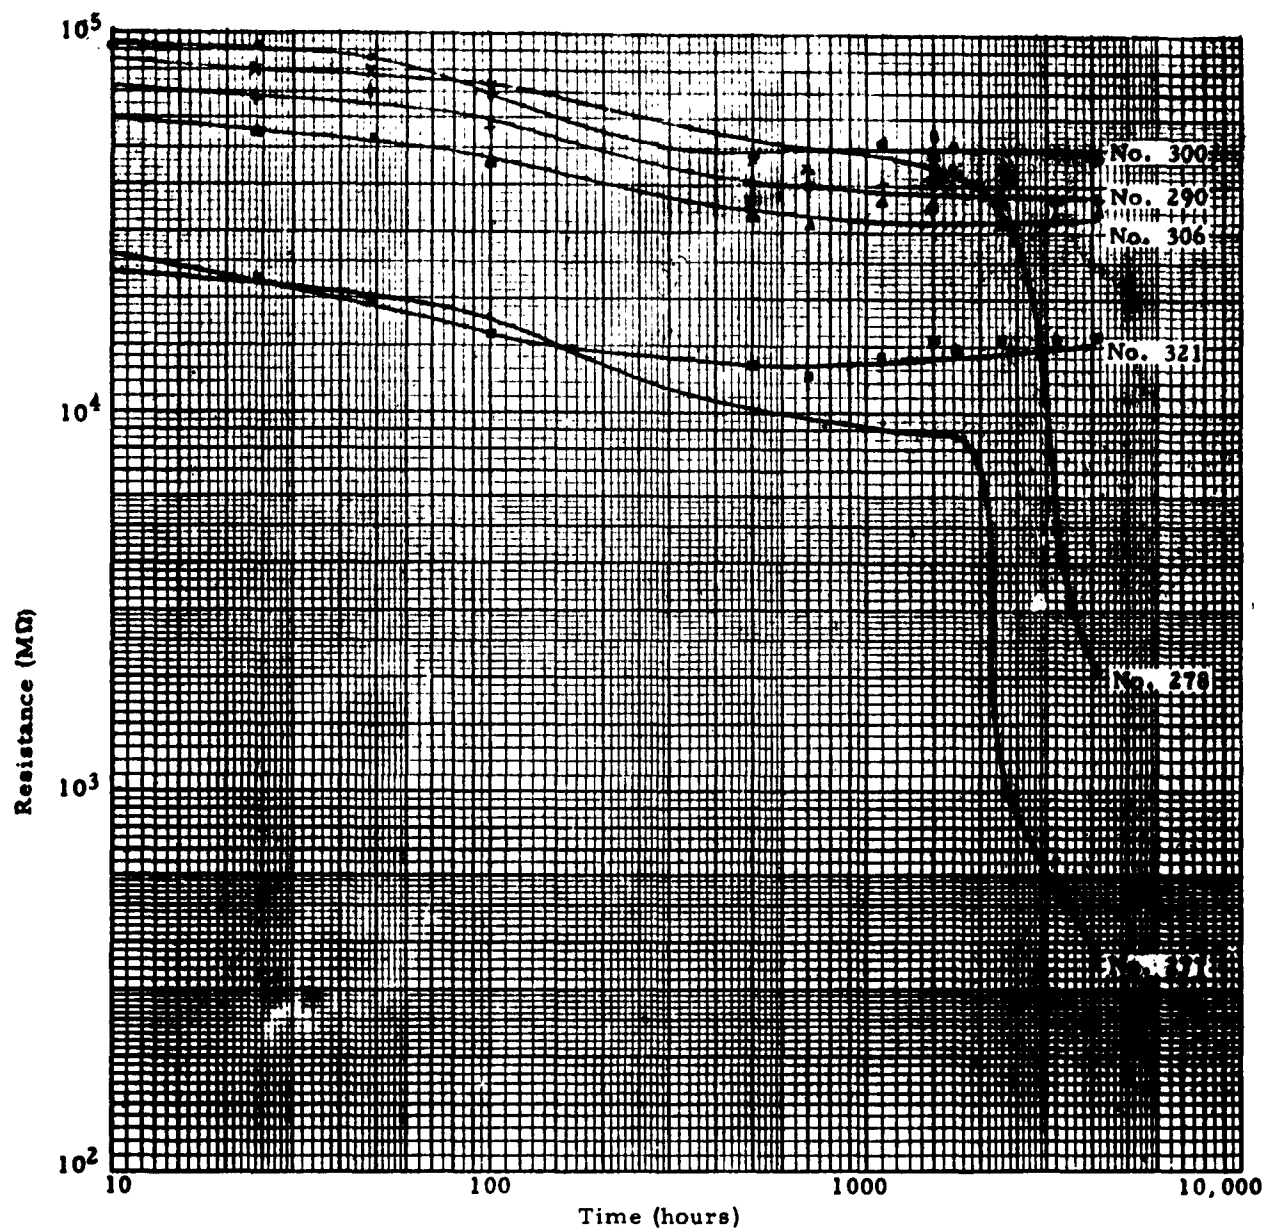

RESISTANCE VS TIME AT 125°C, 400 VDC
FOR 0.01 μ E SIZE I C67 MONOLYTHIC CAPACITORS (Lot 830)

(Capacitors were previously at 125°C, 200 VDC for 2500 hours
and were subjected initially to both steps of screening procedure)

Figure 2

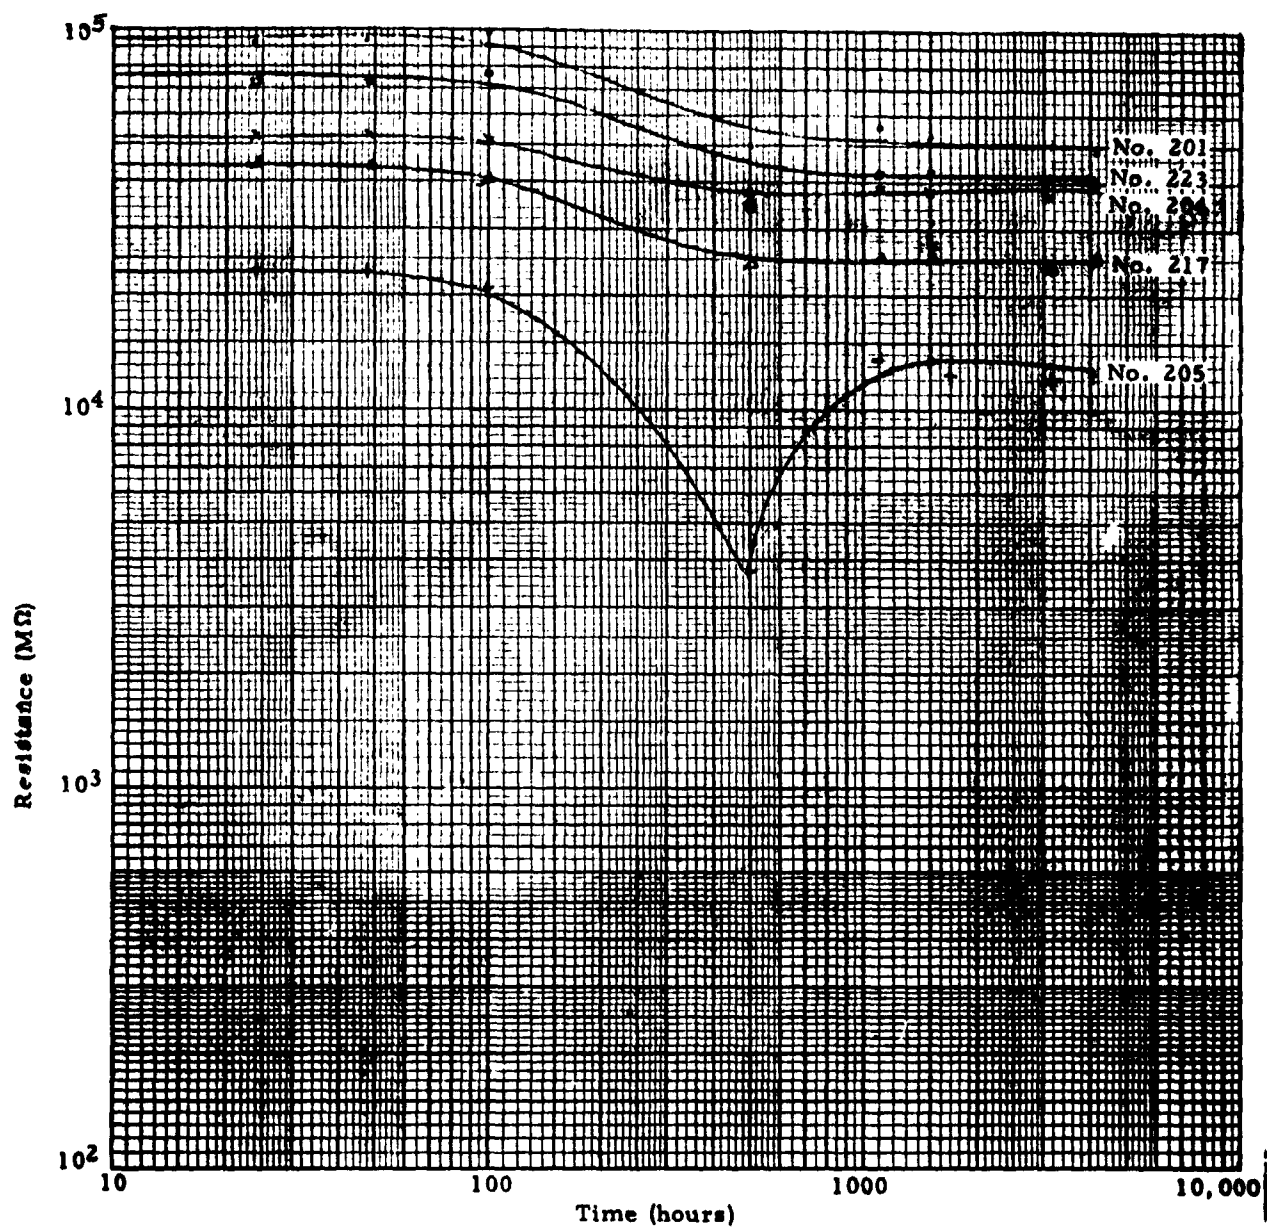

RESISTANCE VS TIME AT 125°C, 400 VDC
FOR 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 830)
(Capacitors were previously at 125°C, 200 VDC for 2500 hours)

Figure 3

increase in temperature in the test oven from 124°C to 127°C. There is no explanation for the behavior of Capacitor No. 205, whose RC product at 150°C, 100 V before life testing was 67 MΩ-μf. This should be compared with the average RC product value of 130 MΩ-μf presented in Figure 18 of the Eighth Quarterly Progress Report.

The behavior of resistance with time for several capacitors which were subjected to Step 1, but not Step 2, of the screening procedure is shown in Figure 4. These capacitors are represented in Positions C and D in Figure 1. Three capacitors, Nos. 246, 253, and 260, were found unacceptable when subjected to Step 1 of the screening procedure. Their behavior in Step 1 was reported in Figure 21 of the Eighth Quarterly Progress Report.

The testing of the 124 capacitors is continuing.


4.3 Voltage-Temperature Matrix

Delivery of 1800 capacitors (0.01 μf) of the improved version to the Sprague test laboratory was completed toward the end of the eleventh quarter. A total of 1500 capacitors will be tested for 10,000 hr. Before placing the capacitors on life test they will be screened, and only potentially long life capacitors will be selected for testing. The number of capacitors to be subjected to the various test conditions is shown in Table 1.

Among the objectives sought in performing the voltage-temperature matrix testing are the statistical derivation of formulas relating lifetime to both these parameters, the statistical evaluation of the screening technique for selecting long-life capacitors, and the determination of the relationship of temperature and voltage to the degradation rate.

Before subjecting the 1800 capacitors (Lot No. 6S9205) to the screening procedure described earlier in this report and then to voltage-temperature matrix testing, it seemed advisable to examine, on a sample basis, the properties of these capacitors and to learn to what degree the properties differ from those of capacitors examined previously.

Figure 5 shows current charging curves at 150°C and 195 V for several of the 1800 capacitors of Lot No. 6S9205 delivered for voltage-temperature matrix testing; Figure 6 presents discharge current curves for the same capacitors. (The equipment and method for measuring charge and discharge current were described in the Fourth Quarterly Progress Report.) Figures 7 and 8 present, respectively, the current charging and discharging curves at 25°C.

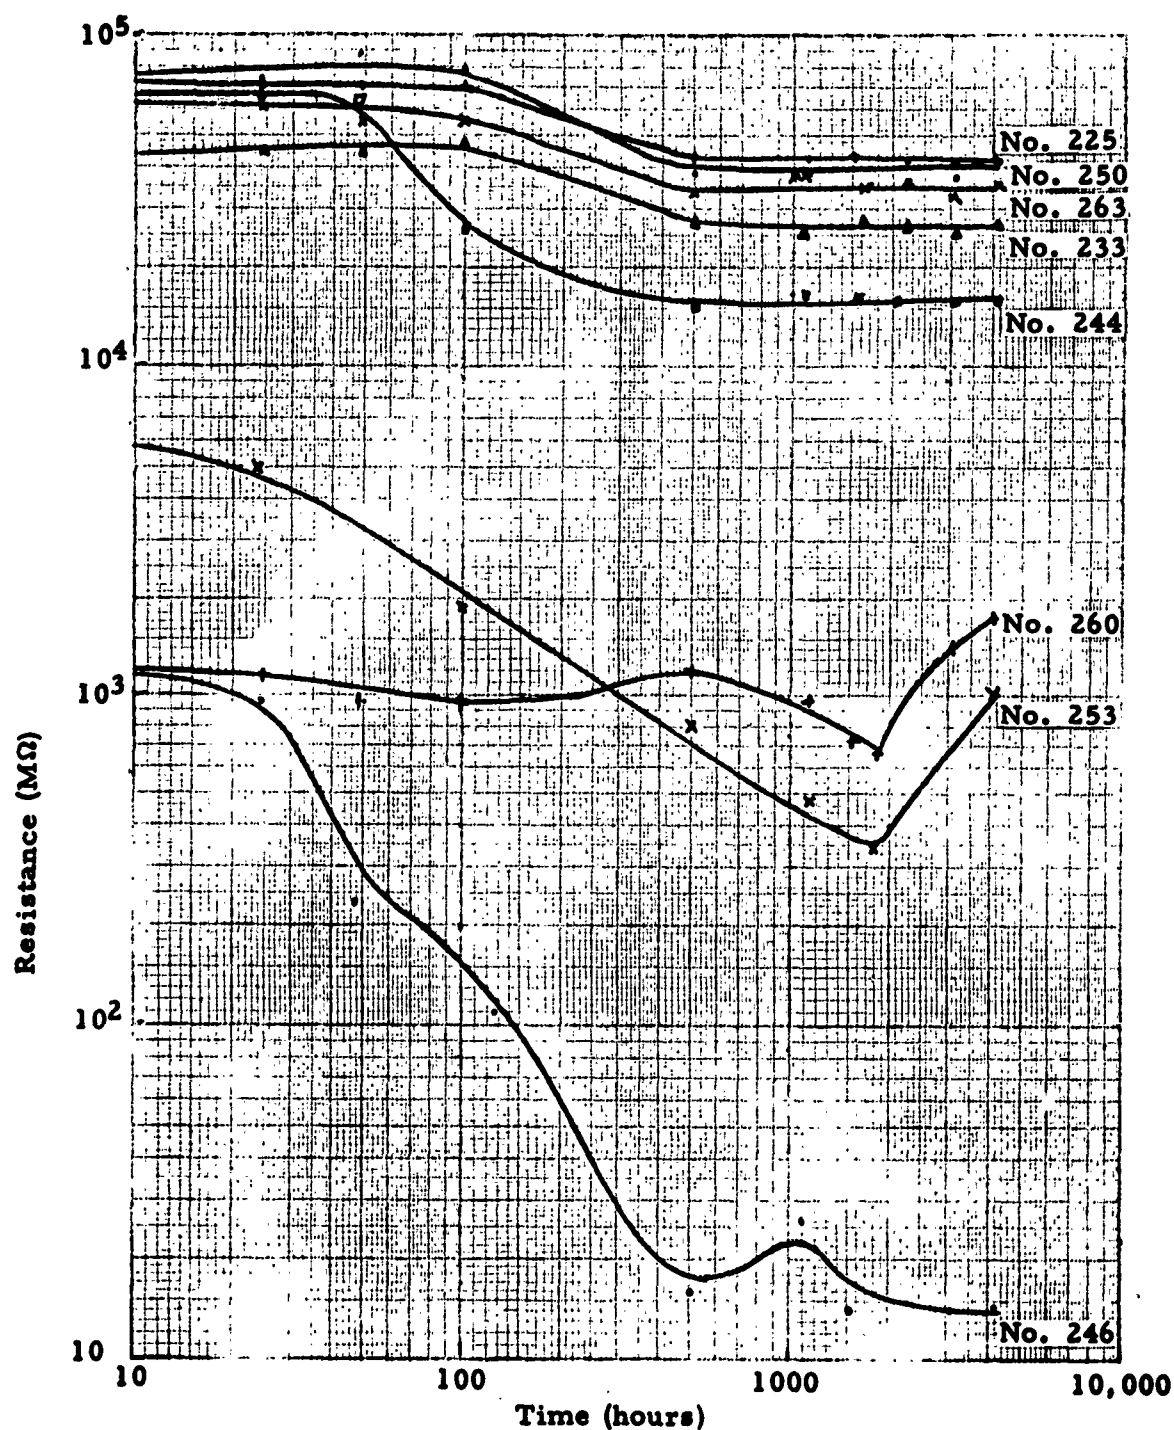


**RESISTANCE VS TIME AT 125°C, 400 VDC
FOR 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 830)**

**(Capacitors were previously at 125°C, 200 VDC for 2500 hours
and were subjected initially to Step 1 of screening procedure)**

Figure 4


TABLE 1
VOLTAGE-TEMPERATURE MATRIX

Voltage	Temperature			
	25°C	85°C	125°C	150°C
25 V			100	
50 V	100	100	100	100
100 V	100	100	300	100
200 V	100	100	100	100

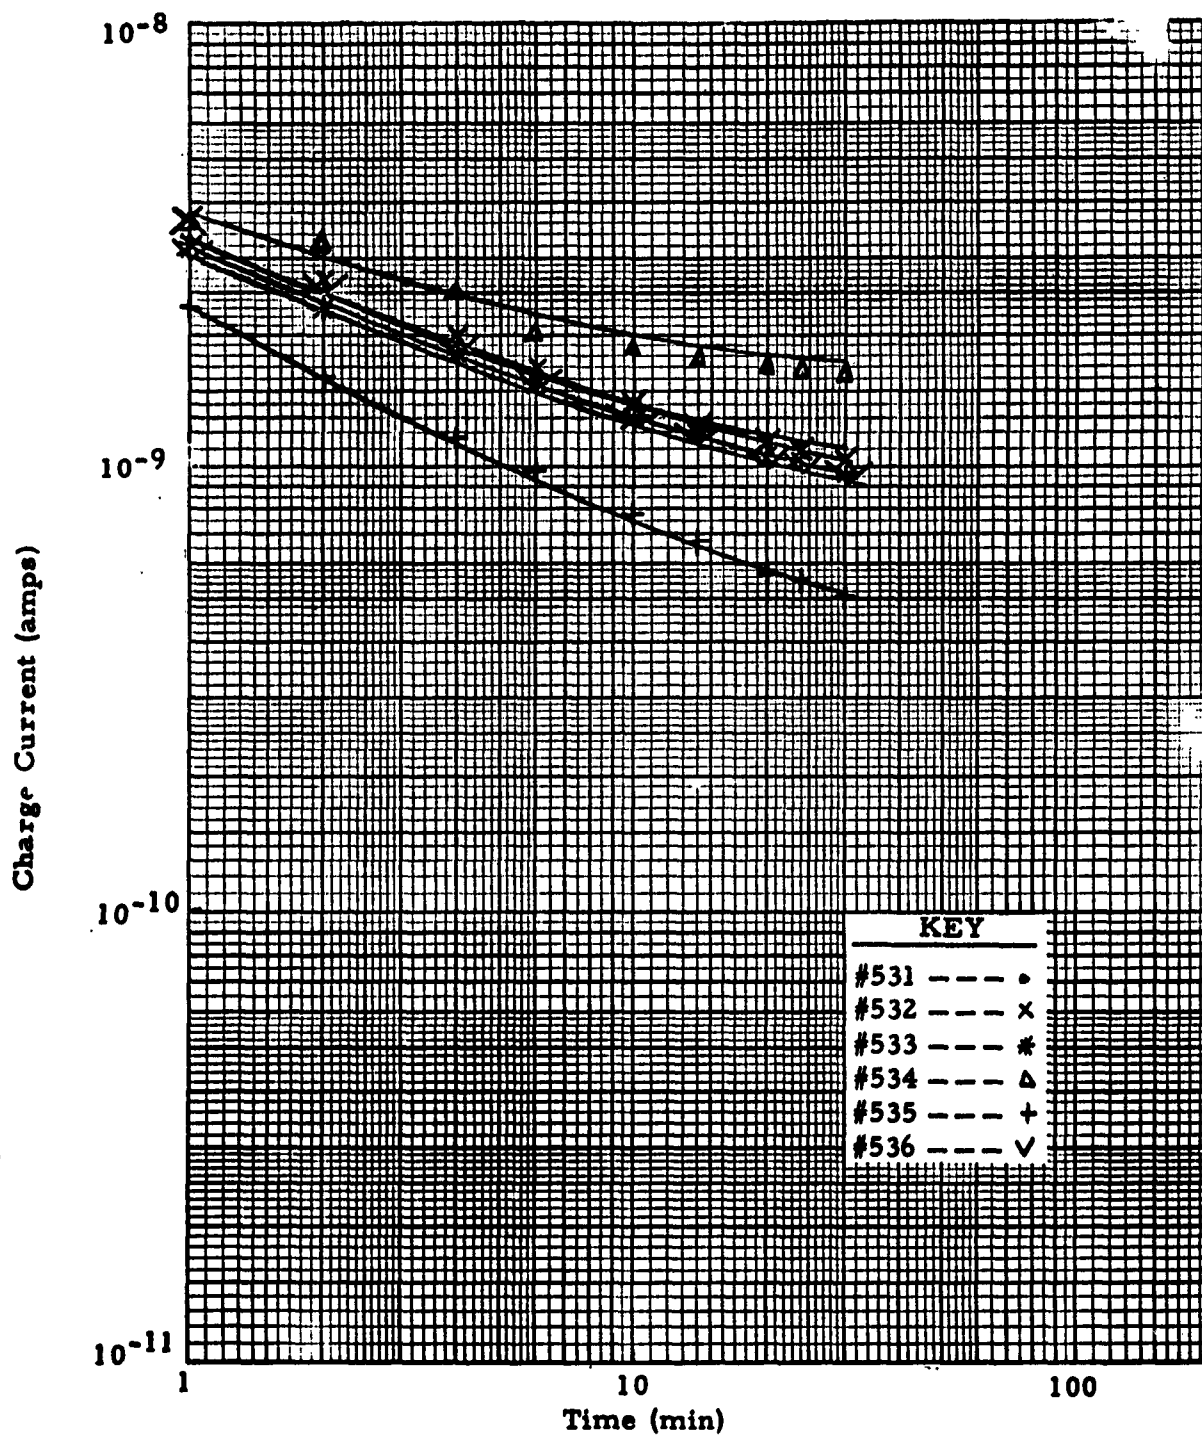


CHARGE CURRENT VS TIME AT 195 VDC, 150°C
FOR IMPROVED 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 6S9205)

Figure 5

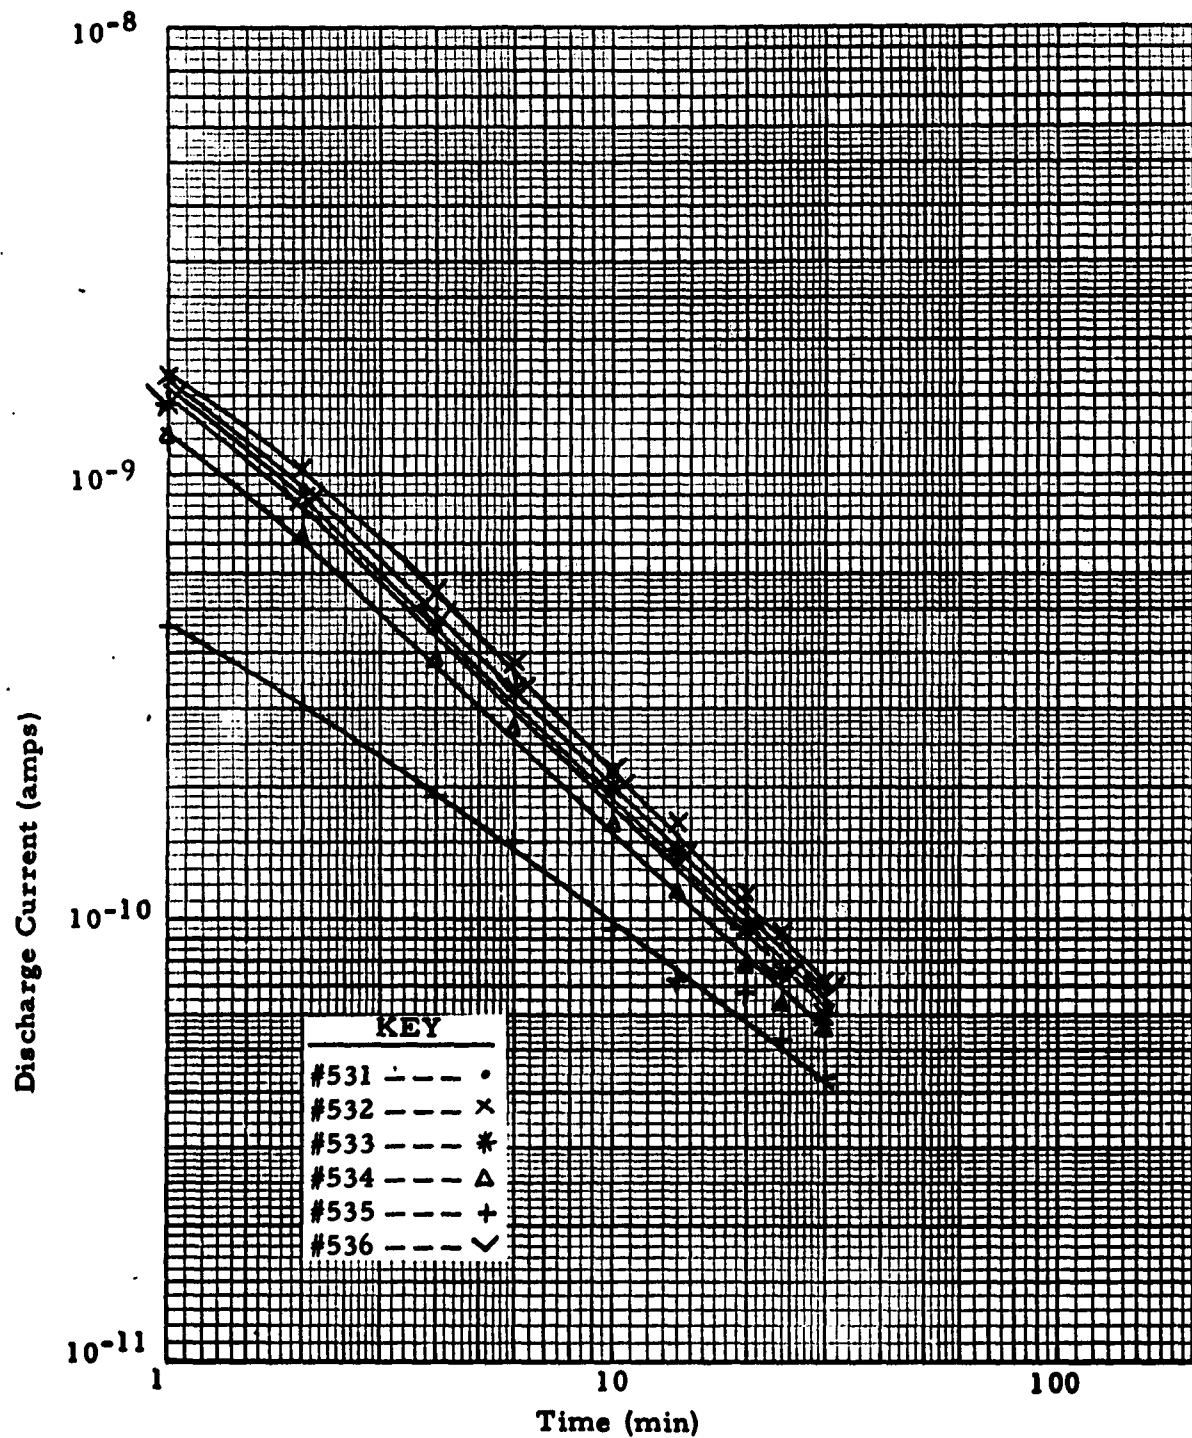


DISCHARGE CURRENT VS TIME AT 150°C
 FOR IMPROVED 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 6S9205)
 (Measured after 30 min charging with 195 VDC)

Figure 6

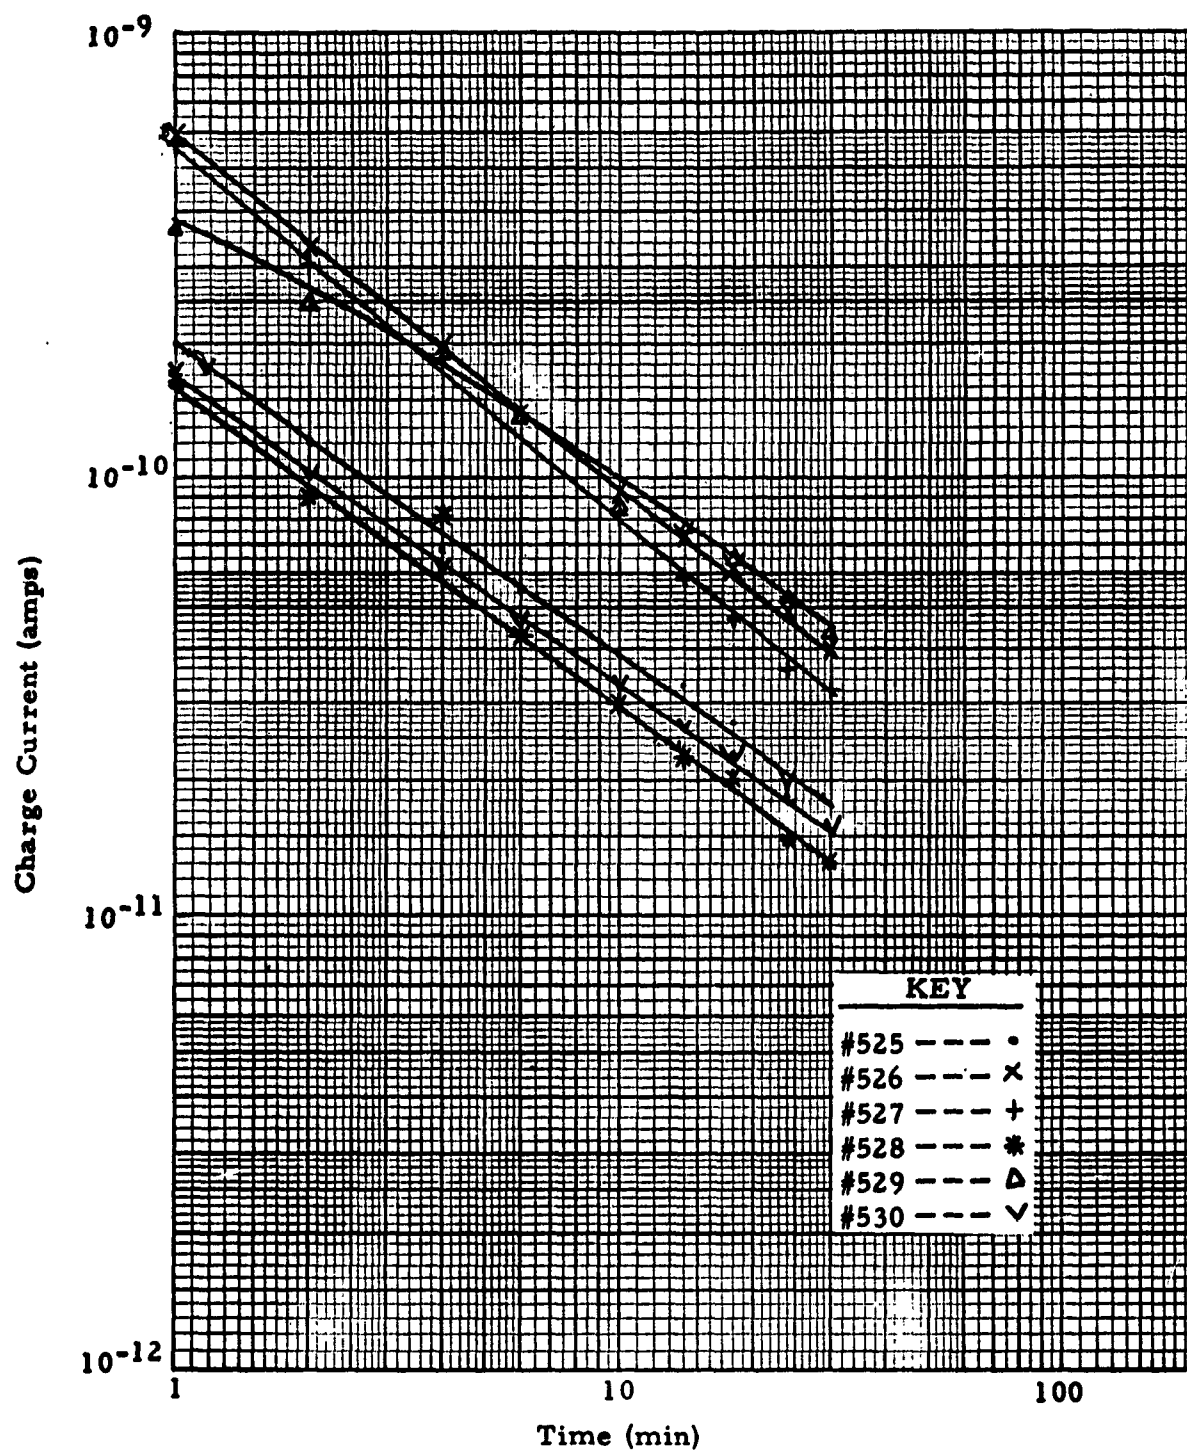

CHARGE CURRENT VS TIME AT 195 VDC, 25°C
FOR IMPROVED 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 6S9205)

Figure 7

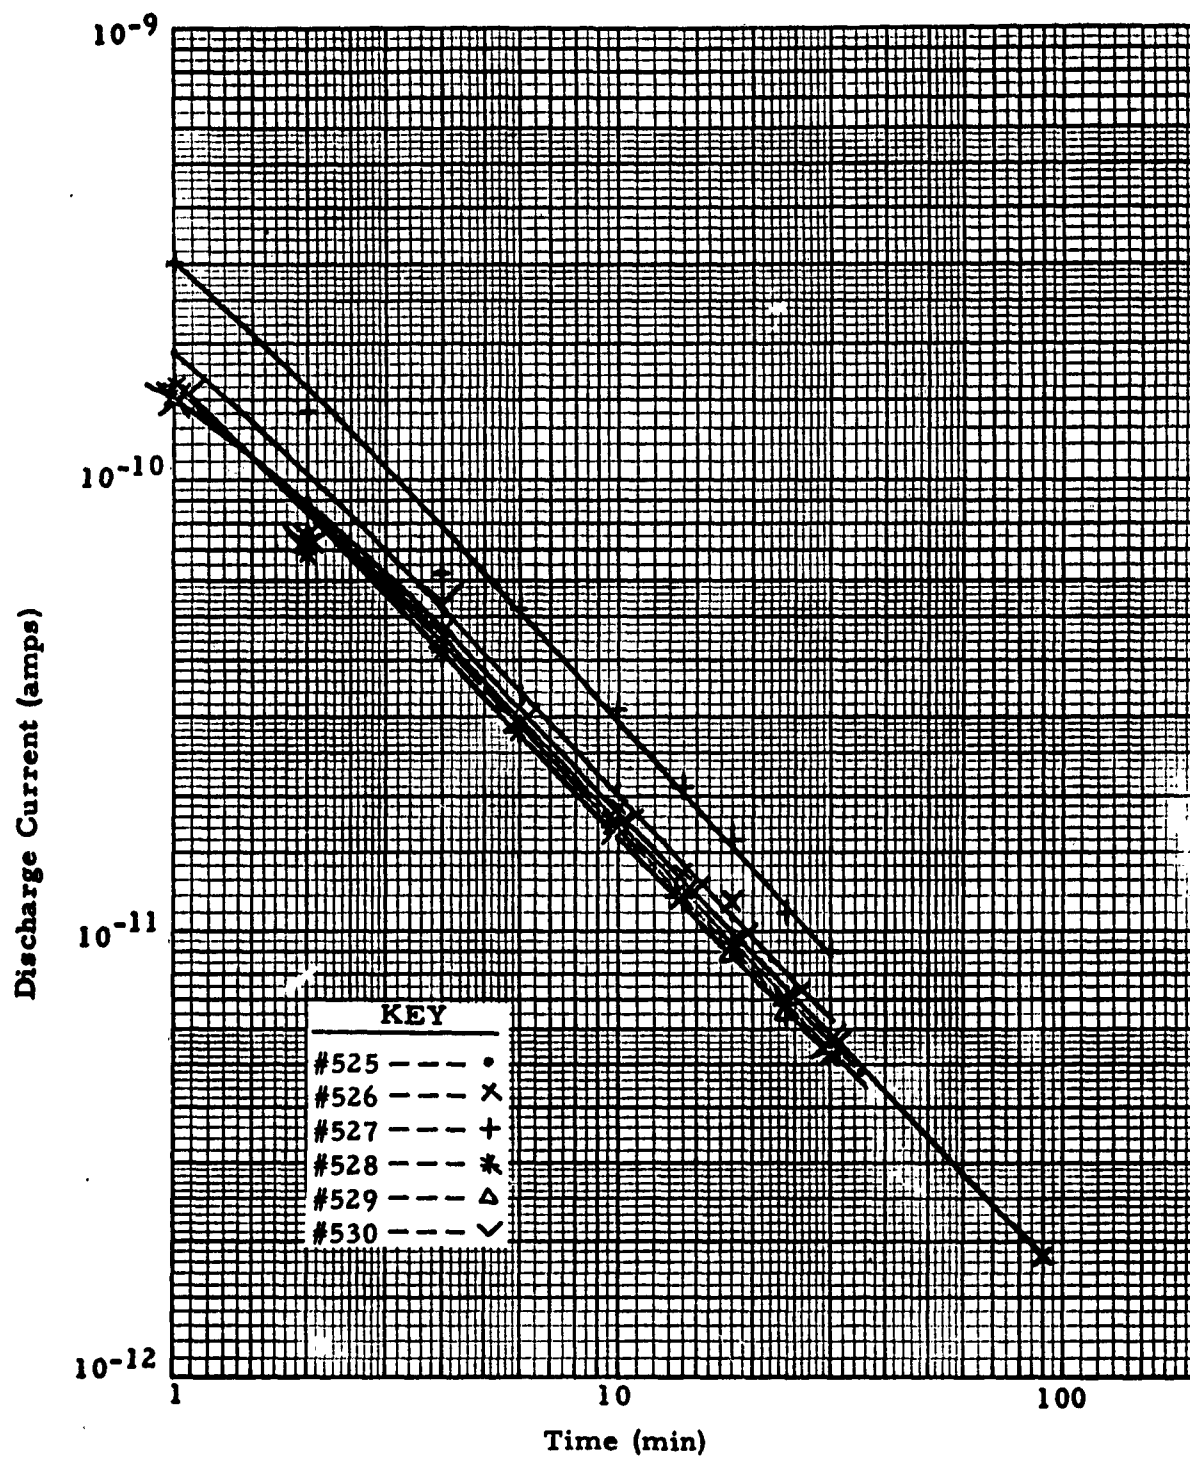

DISCHARGE CURRENT VS TIME AT 25°C
 FOR IMPROVED 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS (Lot 639205)
 (Measured after 30 min charging with 195 VDC)

Figure 8

Figure 9 compares current charging curves on capacitors from Lot No. 6S9205 and from a lot studied earlier. The evident features of the new lot are the greater dielectric absorption and the much lower value of steady-state charging current.

Figure 10 compares resistances of capacitors from three lots for an extended period of time at 150°C and 200 V. It seems probable that Lot No. 6S9205 does not offer the same prospect of longevity as the earlier lot of the improved version, but it appears far superior to the obsolete version. Figure 11 presents resistance with time at 150°C and 195 V for several capacitors from Lot No. 6S9205.

From the foregoing data, it is clear that the screening technique described earlier in this report cannot be applied to Lot No. 6S9205 capacitors unless the technique or conditions are modified. In particular, the condition that resistance not change more than 20% during burn-in for an acceptable capacitor must be relaxed considerably.


An estimate of performance for the majority of the capacitors shown in Figure 11 at other conditions of voltage and temperature may be made using relationships presented in the Eighth Quarterly Progress Report and which are combined into a single expression below:

$$t_1 = t_2 \left[\left(\frac{E_2}{E_1} \right)^n \right] \exp \left[\frac{W}{kT_1} - \frac{W}{kT_2} \right]$$

where,


- t_1 = performance time to be calculated
- t_2 = 160 hr
- E_2 = 195 V
- E_1 = test voltage
- n = 2.7
- W = 0.90 eV
- k = Boltzmann Constant (0.000862 eV/°K)
- T_2 = 423°K (150°C)
- T_1 = test temperature

The following performances are to be considered equivalent as calculated from the above expression.

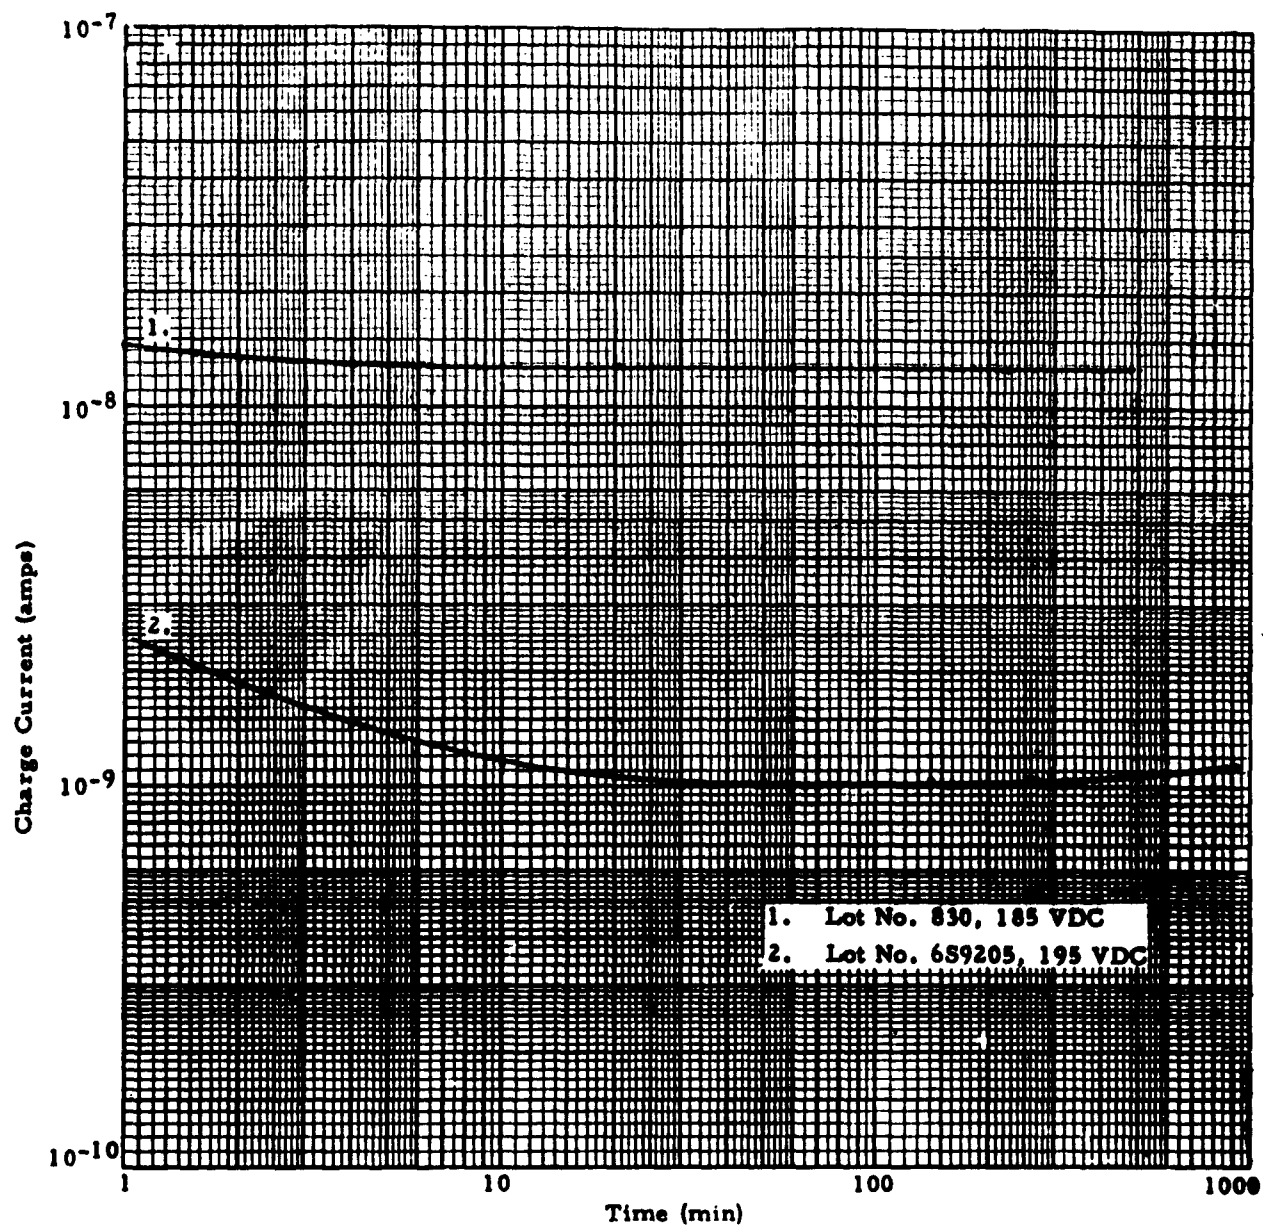


CHARGE CURRENT VS TIME AT 150°C
FOR IMPROVED 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS

Figure 9

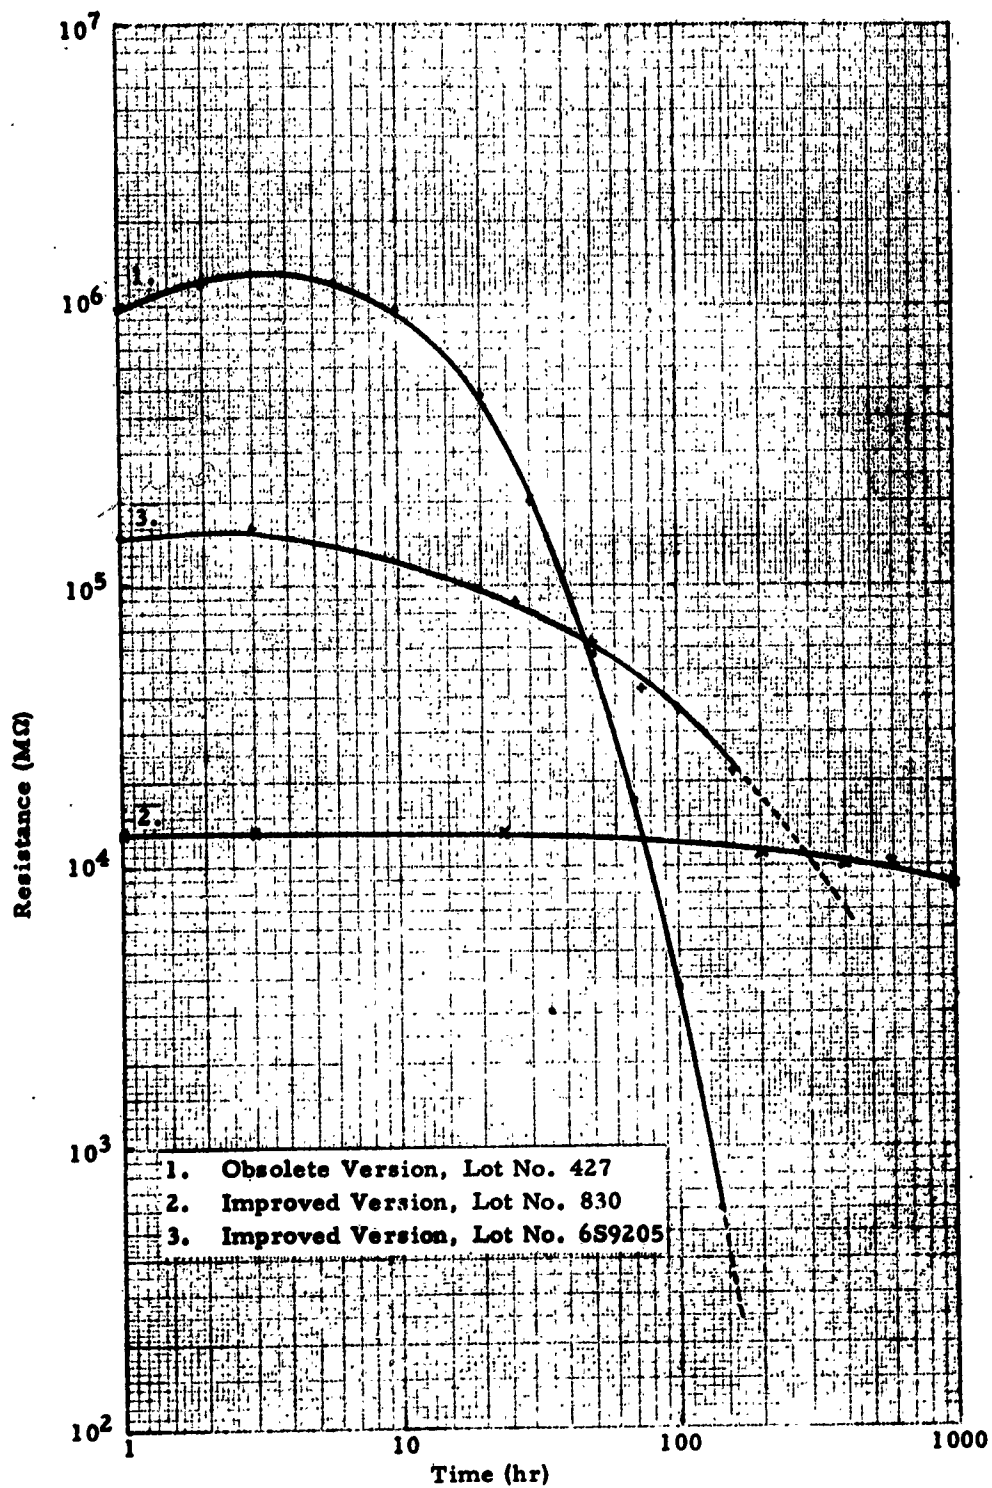

TYPICAL RESISTANCE VS TIME
FOR 0.01 μ f CASE SIZE I C67 MONOLYTHIC CAPACITORS
Conditions: 80 VDC/mil, 150°C

Figure 10

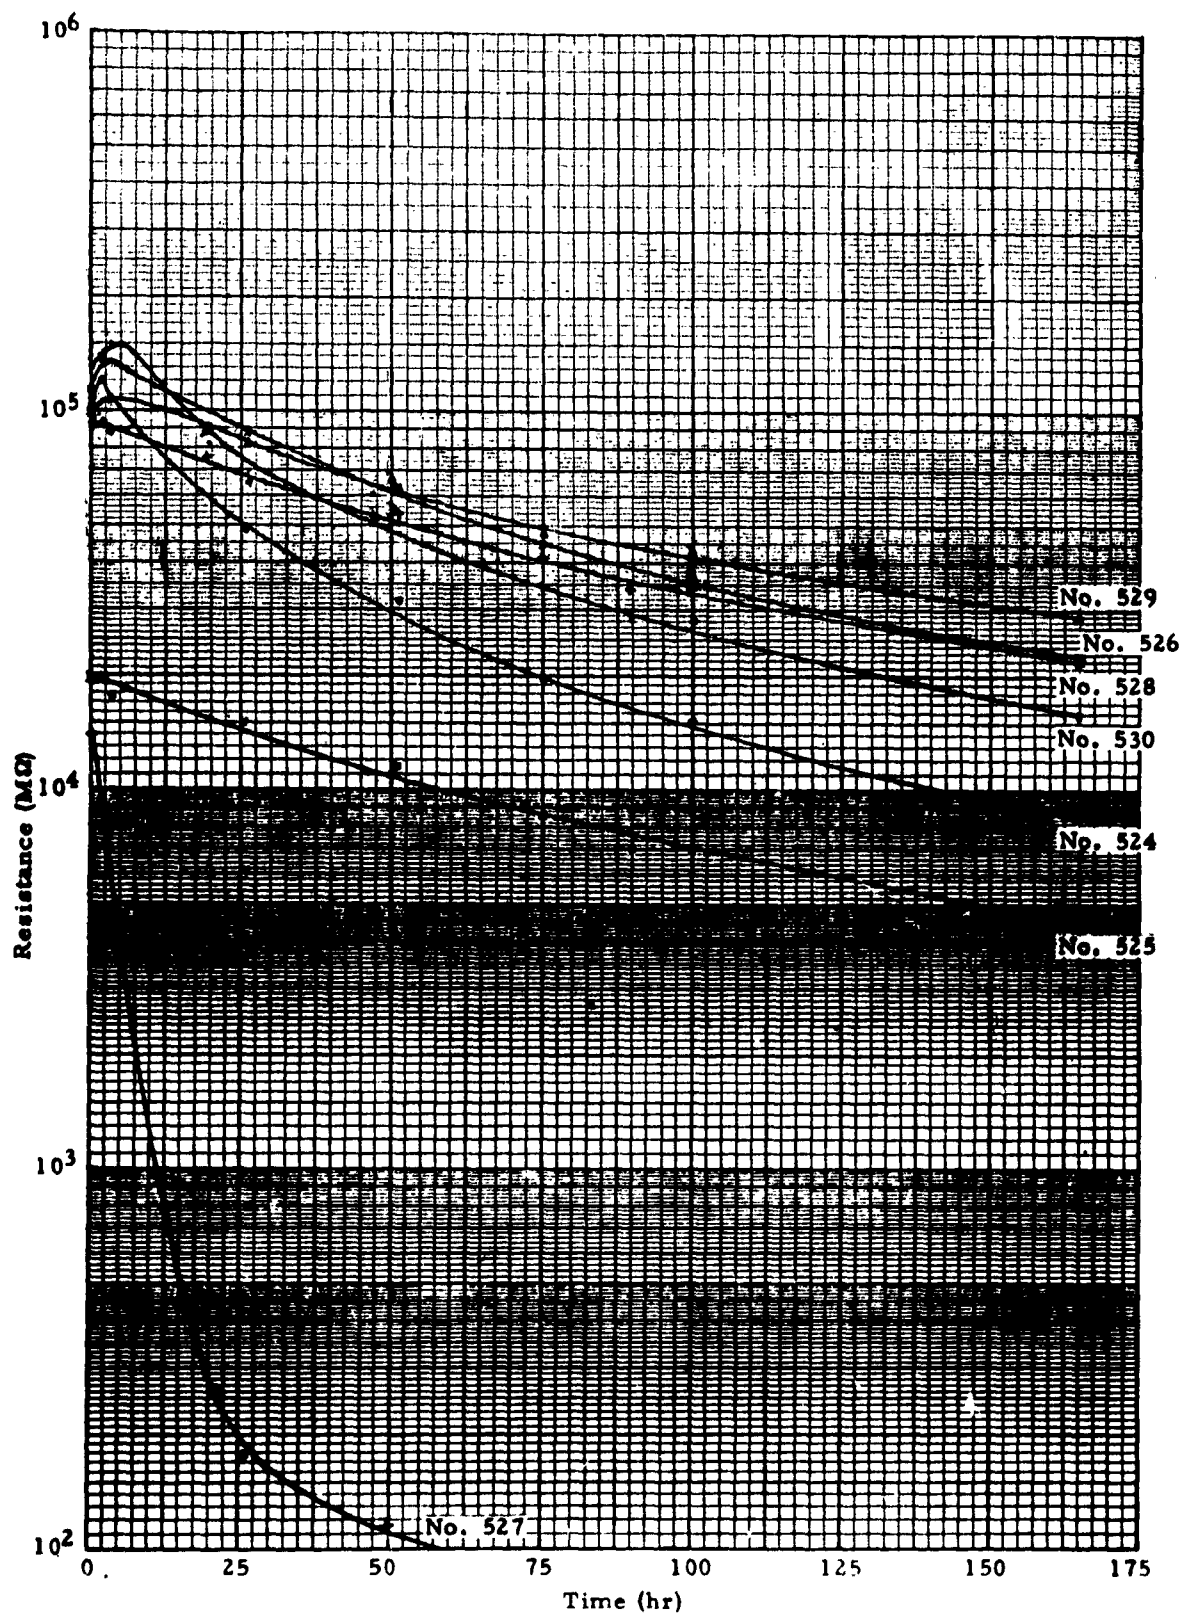

RESISTANCE VS TIME AT 195 VDC, 150°C
FOR 0.01 μ i CASE SIZE 1 C67 MONOLYTHIC CAPACITORS (Lot 6S9205)

Figure 11

<u>Equivalent Performances</u>		
<u>Temperature</u>	<u>Voltage</u>	<u>Time</u>
150°C	195 V	160 hr
125°C	100 V	4,560 hr
125°C	50 V	29,700 hr
85°C	200 V	13,200 hr
85°C	100 V	36,000 hr

Examination of Lot No. 6S9205 capacitors will be continued to determine the criteria to be used for selecting potentially long-life capacitors.

4.4 Capacitors Having 1.5 Mil Dielectric Layers

The 0.022 μ f C67 Case Size I MONOLYTHIC capacitors having 1.5 mil dielectric layers have not yet been manufactured.

SECTION 5

CONCLUSIONS

- (1) The testing of 124 of the improved version of the 0.01 μf C67 Case Size I MONOLYTHIC capacitor under the new test conditions of 125°C and 400 VDC has now gone 4000 hr. Two of the 53 capacitors which passed both parts of the screening program are showing marked degradation.
- (2) Lot No. 6S9205, consisting of 1800 capacitors (0.01 μf) of the improved version, was received during this period. Examination of these capacitors, on a sample basis, showed greater dielectric absorption and a much lower value of steady-state charging current. These preliminary tests also indicated that this lot cannot be subjected to the two-part screening program unless the screening technique or conditions are modified.
- (3) Manufacture of 0.022 μf C67 Case Size I capacitors with dielectric layers 1.5 mils thick has not yet been completed.

SECTION 6
PROGRAM FOR NEXT QUARTER

- (1) Examination of the 1800 C67 Case Size I MONOLYTHIC capacitors will be completed to determine criteria to be used for selecting potential long-life capacitors for voltage-temperature matrix testing.
- (2) Voltage-temperature matrix testing will begin.

SECTION 7
DISTRIBUTION LIST

Copies

1	Office of the Assistant Secretary of Defense (R&E) Room 3E1065 The Pentagon Washington 25, D. C. ATTN: Technical Library
2	Chief of Research and Development Department of the Army Washington 25, D. C.
2	Commanding General U. S. Army Materiel Command Washington, D. C. 20315 ATTN: R & D Directorate
10	Commander, Defense Documentation Center Cameron Station, Building 5 Alexandria, Virginia 22314 ATTN: TISIA
1	Commanding Officer U. S. Army Combat Developments Command Fort Belvoir, Virginia ATTN: CDCMR-E
1	Commanding General U. S. Army Combat Developments Command Communications-Electronics Agency Fort Huachuca, Arizona
2	Chief, U. S. Army Security Agency Arlington Hall Station Arlington 12, Virginia ATTN: ACoIS, Gs (Technical Library)

Copies

1	Deputy President U. S. Army Security Agency Board Arlington Hall Station Arlington 12, Virginia
1	Commanding Officer Harry Diamond Laboratories Connecticut Avenue & Van Ness St., N. W. Washington 25, D. C.
1	Director, U. S. Naval Research Laboratory Washington, D. C. 20390 ATTN: Code 2027
1	Commanding Officer and Director U. S. Navy Electronic Laboratory San Diego 52, California ATTN: Library
1	Systems Engineering Group (SEPIR) Wright-Patterson Air Force Base, Ohio 45433
1	Director, Materiel Readiness Directorate Hq, U. S. Army Electronics Command Fort Monmouth, New Jersey 07703 ATTN: AMSEL-MR
2	Air Force Cambridge Research Laboratories L. G. Hanscom Field Bedford, Massachusetts ATTN: CRXL-R
2	Electronic Systems Division (AFSC) Scientific & Technical Information Division (ESTI) L. G. Hanscom Field Bedford, Massachusetts 01731
1	Rome Air Development Center Griffiss Air Force Base, New York ATTN: RAALD
3	Advisory Group on Electron Devices 346 Broadway, 8th Floor New York, New York 10013

Copies

1	AFSC Scientific/Technical Liaison Office U. S. Naval Air Development Center Johnsville, Pennsylvania
1	USAEL Liaison Office Rome Air Development Center Griffiss Air Force Base, New York 13442 ATTN: RAOL
1	NASA Representative (SAK/DL) Scientific and Technical Information Facility P. O. Box 5700 Bethesda, Maryland 20014
1	Commander U. S. Army Research Office (Durham) Box CM - Duke Station Durham, North Carolina
2	Commanding Officer U. S. Army Engineer Research & Development Laboratories Fort Belvoir, Virginia 22060 ATTN: STINFO Branch
1	Marine Corps Liaison Office U. S. Army Electronics Laboratories Fort Monmouth, New Jersey 07703 ATTN: AMSEL-RD-LNR
1	AFSC Scientific/Technical Liaison Office U. S. Army Electronics Laboratories Fort Monmouth, New Jersey 07703 ATTN: AMSEL-RD-LNA
1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey 07703 ATTN: AMSEL-RD-DR/DE
1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey 07703 ATTN: Technical Documents Center

Copies

1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey 07703 ATTN: AMSEL-RD-ADO-RHA
1	Commanding Officer U. S. Army Electronics Research & Development Activity White Sands, New Mexico 88002 ATTN: AMSEL-RD-WS-A
1	Hq, U. S. Army Electronics Command Commodity Management Office Fort Monmouth, New Jersey 07703 ATTN: AMSEL-TE
1	Commander Rome Air Development Center Griffiss Air Force Base, New York ATTN: Mr. L. J. Gubbins, RASGR
1	Chief, Bureau of Ships Department of the Navy Washington 25, D. C. ATTN: Code 681A2A (J. M. Kerr, Jr.)
1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey ATTN: AMSEL-RD-PE (Division Director)
1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey ATTN: AMSEL-RD-P (Department Director)
1	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey ATTN: AMSEL-RD-PE (Dr. E. Both)
(Balance of copies)	Director U. S. Army Electronics Laboratories Fort Monmouth, New Jersey ATTN: AMSEL-RD-PEE (J. Allen)

SECTION 8
IDENTIFICATION OF PERSONNEL

<u>Personnel</u>	<u>Hours</u>
C. Belouin	3.0
C. Boyer	3.5
O. Buyomaster	8.0
J. Fabricius	10.0
D. Folster	4.5
R. Kemper	8.0
P. Kennedy	6.5
H. La Bombard	32.0
H. Lombard	6.25
G. Morse	48.25
C. Nielsen	11.5
T. Prokopowicz	9.0
F. Schoenfeld	24.0
C. Shepard	20.5
E. Taff	3.5
L. Therrien	48.0
A. Zito	15.5
Total	262.0

Unclassified
Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author)		2a. REPORT SECURITY CLASSIFICATION
Sprague Electric Company North Adams, Massachusetts		Unclassified
		2b. GROUP
3. REPORT TITLE		
Intrinsic Reliability Subminiature Ceramic Capacitors		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)		
Eleventh Quarterly Progress Report, 1 Dec 64 - 28 Feb 1965		
5. AUTHOR(S) (Last name, first name, initial)		
Kennedy, Patrick M. and Prokopowicz, Thomas I.		
6. REPORT DATE	7a. TOTAL NO. OF PAGES	7b. NO. OF REFS
	22	
8a. CONTRACT OR GRANT NO.		9a. ORIGINATOR'S REPORT NUMBER(S)
DA 36-039-SC-90705		
b. PROJECT NO.		
IP6 24001 A 057		
c. IP6 24001 A 057 01		9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)
d. 01519-81		
10. AVAILABILITY/LIMITATION NOTICES		
Qualified Requestors may obtain copies of this report from DDC. Foreign announcement and dissemination of this report by DDC is not authorized.		
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY
		U. S. Army Electronics Command Fort Monmouth, N. J. (AMSEL-RD-PEE)
13. ABSTRACT		
Testing of C67 Case Size I Monolithic capacitors of the improved version continues to demonstrate the long-life capability of this capacitor at use conditions. The testing of 124 of these capacitors at 200 VDC and 125°C for 2500 hours without catastrophic failure, then at 400 VDC and 125°C for 4000 hours with only five displaying any degradation, continues to indicate the intrinsic high reliability of this unit. Some properties of 1800 capacitors (0.01 μf rating) prepared for the voltage temperature matrix testing were examined.		

DD FORM 1 JAN 64 1473

Unclassified
Security Classification

Unclassified
Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Long-life capability Reliability Improved Capacitor Charge Current Discharge Current Resistance Screening Technique						

INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parentheses immediately following the title.

4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. AUTHOR(S): Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. REPORT DATE: Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.

8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. OTHER REPORT NUMBER(S): If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical content. The assignment of links, rules, and weights is optional.

Unclassified
Security Classification