


AD

AD 682740



DDC
RECEIVED
FEB 1 / 1969
RECEIVED
B

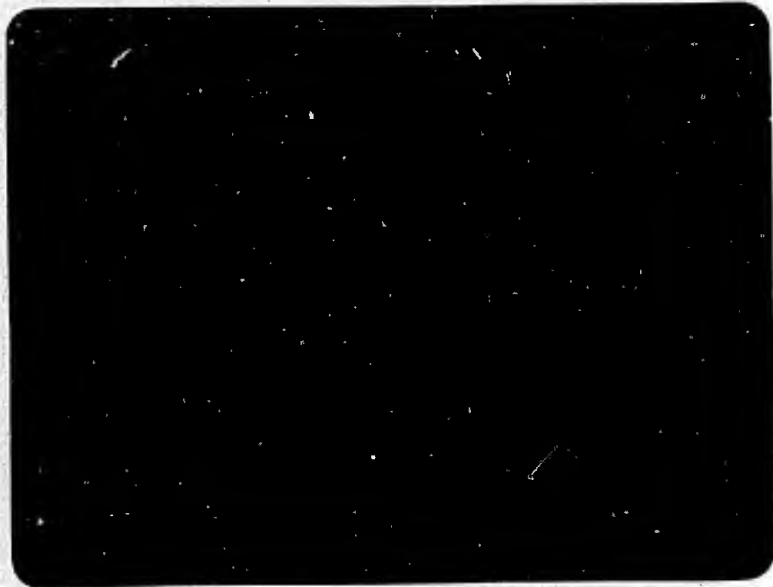

Reproduced by the
CLEARINGHOUSE
for Federal Scientific & Technical
Information Springfield Va. 22151

Watertown, Massachusetts 02172

ARMY MATERIALS AND MECHANICS RESEARCH CENTER

AMMRC TR 68-22

**ANODIC POLARIZATION OF TITANIUM AND
ITS ALLOYS IN HYDROCHLORIC ACID**

Technical Report by

MILTON LEVY and GILBERT N. SKLOVER

November 1968

This document has been approved for public
release and sale; its distribution is unlimited.

D/A Project 1C024401A328
AMCMS Code 5025.11.294
Metals Research for Army Materiel
Subtask 38081

METALS LABORATORY
ARMY MATERIALS AND MECHANICS RESEARCH CENTER
WATERTOWN, MASSACHUSETTS 02172

ARMY MATERIALS AND MECHANICS RESEARCH CENTER

ANODIC POLARIZATION OF TITANIUM AND ITS ALLOYS IN HYDROCHLORIC ACID

ABSTRACT

Commercially pure titanium and the alloys studied exhibited active to passive transitions in HCl. Increasing the acid concentration increased the critical current for passivity and shifted the critical potential for passivity in the noble direction. Increasing the temperature served only to increase the critical current for passivity. Activation energies for the anodic polarization process were the right order of magnitude for a reaction controlled by reactivity at the metal surface. For the alpha-beta alloy 6Al-6V-2Sn the critical current for passivity increased as the ratio of amounts of beta-to-alpha phase decreased with increasing strength level. The dissolution is accelerated, probably by the galvanic effects and the unfavorable area ratio. Ti-75A, a commercially pure metal, had a smaller critical current for passivity value than did the alloys, which was expected. Secondary current density increases were observed for all the alloys at potentials above +1.0 v. For the 13V-11Cr-3Al alloy such behavior was attributed to transpassivity. For the other alloys the phenomena was attributed to pitting or localized corrosion. The commercially pure metal remained passive in this potential range. The addition of Fe^{3+} and Cu^{2+} (0.03 M) to the HCl facilitated passivation of the metal and its alloys. The maximum dissolution current densities for the metal and alloys in HCl were double those in H_2SO_4 . Pitting of several of the alloys occurred in HCl but not in H_2SO_4 .

CONTENTS

	Page
ABSTRACT	
INTRODUCTION	1
EXPERIMENTAL PROCEDURE	1
RESULTS AND DISCUSSION	
Polarization of Ti-6Al-6V-2Sn	2
Polarization of Commercially Pure Ti-75A	4
Polarization of Ti-8Al-1Mo-1V	6
Polarization of Ti-13V-11Cr-3Al	6
Polarization of Ti-6Al-4V	8
Comparison of Polarization Behavior of Titanium and Alloys	8
SUMMARY	11

BLANK PAGE

INTRODUCTION

In previous work¹ the anodic behavior of alpha-beta titanium alloy 6Al-6V-2Sn was studied in sulfuric acid as a function of temperature, acid concentration, selected ion additions to the electrolyte, yield strength level, and microstructure of the alloy. For comparison, commercially pure alpha titanium and a beta alloy containing 13V-11Cr-3Al were also studied. The present investigation extends this study to hydrochloric acid media, additional commercially available titanium alloys, and considers the directionality of the metal specimen.

EXPERIMENTAL PROCEDURE

The metal and alloys studied were commercially pure alpha-Ti-75A in the annealed condition, alpha-beta Ti-6Al-6V-2Sn heat treated to strength levels of 140, 160, and 180 ksi, beta Ti-13V-11Cr-3Al in the as-received mill-annealed condition, alpha-beta Ti-8Al-1Mo-1V in both the single and duplex annealed condition, and annealed alpha-beta Ti-6Al-4V alloy.

The potential sweep method of potentiostatic polarization (sometimes called potentiodynamic polarization) was used. The electrode potential was continuously changed at a constant rate of 5,000 mv/hr (83.3 mv/min) and current was simultaneously recorded. A Wenking Potentiostat in conjunction with a motor potentiometer for automatic programming of the operating potential and an x-y recorder were employed to automatically record current versus voltage. The automatic potential sweep technique (as opposed to potential step) yields the most reproducible results because of the high resolution offered by continuous recording. The polarization cell and general procedure has been described previously.¹

Polarization measurements were made in 5, 12, and 20 percent hydrogen-saturated hydrochloric acid electrolytes at temperatures of 35, 50, and 65 C $\pm$ 1 degree.

For the directionality studies cylindrical specimens of 1 sq cm surface area were machined both parallel (longitudinal) and perpendicular (transverse) to the working direction. Because of the many similarities in behavior, a number of the polarization curves obtained are not presented.

¹LEVY, M. *Anodic Behavior of Titanium and Commercial Alloys in H₂SO₄*. Corrosion, v. 23, no. 8, 1967, p. 236-244; also Army Materials and Mechanics Research Center, AMRA TR 67-16, May 1967.

RESULTS AND DISCUSSION

Polarization of Ti-6Al-6V-2Sn

Effect of Concentration of Electrolyte

Figure 1 shows the anodic behavior of Ti-6Al-6V-2Sn (180 ksi strength level) at 65 C in 5, 12, and 20 percent HCl. Increasing the acid concentration increases the critical current for passivity or maximum dissolution current and the critical potential for passivity is shifted in the more noble direction. Similar behavior was observed at other strength levels and temperatures except at the lowest temperature (35 C) where the curves were characterized by the extremely small currents required to passivate the alloy and the negligible extent of their active regions.

Effect of Temperature

The critical current for passivity for the alloy (140, 160, 180 ksi strength levels) in 5, 12, and 20 percent HCl increases considerably as temperature is increased from 35 C to 65 C. The critical potential for passivity is unaffected. Figure 2 shows log critical current for passivity plotted against the reciprocal of absolute temperature. The result is a linear dependency which can be expressed by the Arrhenius equation and an activation energy of 21 kcal/mol calculated. This activation energy is the right order of magnitude for a reaction controlled by chemical reactivity at the surface rather than a diffusion-controlled reaction.

Effect of Strength Level

Anodic polarization curves for Ti-6Al-6V-2Sn at strength levels of 140, 160, and 180 ksi in 20 percent HCl at 65 C are shown in Figure 3. The critical current for passivity increases with increasing strength level. The critical passive potential is unchanged. X-ray diffraction analysis showed that the beta-phase content decreases from 36 to 23 to 17 percent with a corresponding increase in alpha phase as the strength level increases from 140 to 160 to 180 ksi. It is probable that the alloying additions produce a significant potential difference between the alpha and beta phases which causes the relatively high dissolution currents. The dissolution current increases as the ratio of amounts of beta to alpha phases decreases with increasing strength level. Dissolution may be accelerated both by the galvanic effects and the unfavorable area ratio.

Effect of Iron and Copper Additions

Fe^{3+} and Cu^{2+} were added to the HCl electrolyte in the form of FeCl_3 and CuSO_4 . Figure 4 shows the effect of the Fe addition on the polarization behavior of Ti-6Al-6V-2Sn (180 ksi) in 20 percent HCl at 65 C. The critical current for passivity decreases with increasing Fe concentrations. At all concentrations of Fe there is some inhibition of the anodic reaction. At the maximum Fe concentration (0.03 M) the polarization current becomes negative

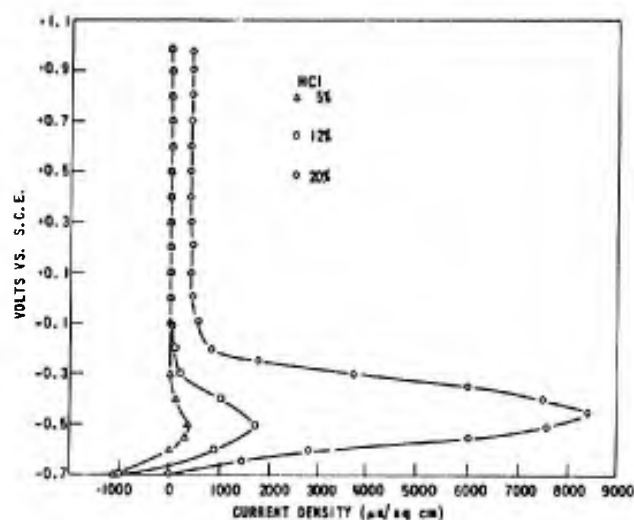


Figure 1. EFFECT OF CONCENTRATION OF HCl ON POLARIZATION OF Ti-6Al-6V-2Sn (180 KSI) AT 65 C

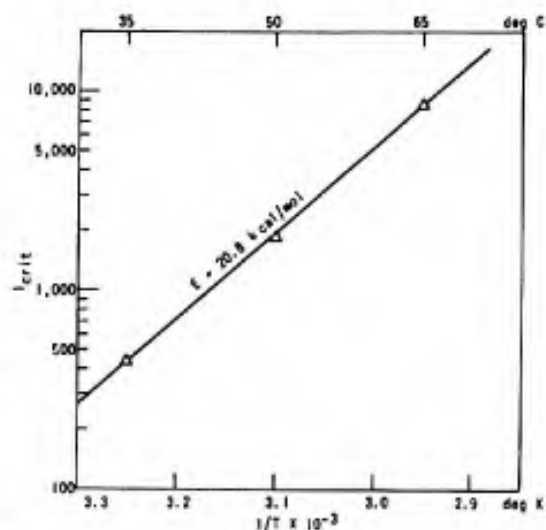


Figure 2. ARRHENIUS PLOT FOR Ti-6Al-6V-2Sn (180 KSI) IN 20% HCl

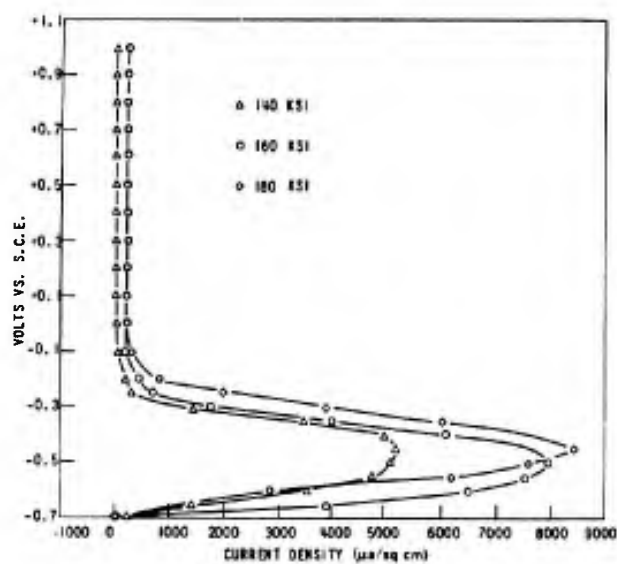


Figure 3. EFFECT OF STRENGTH LEVEL ON POLARIZATION OF Ti-6Al-6V-2Sn IN 20% HCl AT 65 C

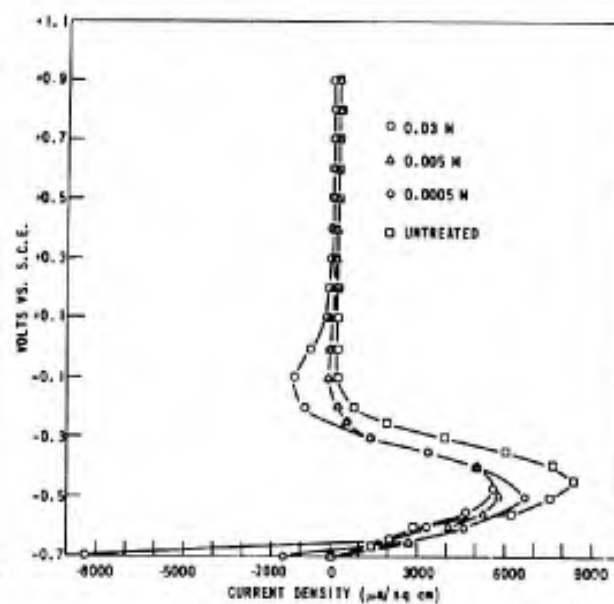


Figure 4. EFFECT OF FeCl_3 CONCENTRATION ON POLARIZATION OF Ti-6Al-6V-2Sn (180 KSI) IN 20% HCl AT 65 C

and recrosses the zero current to a positive value at some point in the passive range. This behavior indicates that passivity is stable and a stable passive potential exists. The electrochemical process associated with the cathodic currents is probably hydrogen ion reduction, particularly because the cathodic current occurred at a potential more active than the hydrogen electrode value of the electrolyte. The effect of cupric ions on the polarization behavior of the alloy in 20 percent HCl at 65 C is shown in Figure 5. The Cu^{2+} ion reduces the critical current for passivity. The reduction increases with increasing Cu^{2+} concentration. At 0.03 M concentration the maximum dissolution current is approximately one third that of the untreated solution. The Cu^{2+} ion achieves greater inhibition than the Fe^{3+} ion.

Polarization of Commercially Pure Ti-75A

Effect of Concentration of HCl

Figure 6 shows anodic polarization curves for Ti-75A in 5, 12, and 20 percent HCl at 65 C. The maximum dissolution current increases with increasing HCl concentration. The critical potential for passivity is essentially the same in both 12 and 20 percent solutions. At the lowest HCl concentration, the curve is characterized by the negligible extent of the active region and a very small current is required to passivate the metal. At a potential of +1.5 v different behavior is observed in 5 percent HCl solution. A secondary active-passive transition is observed. Although Levy¹ reported transpassive behavior for Ti-13V-11Cr-3Al in H_2SO_4 , transpassivity has not been reported for commercially pure titanium. Why it should occur only in 5 percent HCl is not understood. Perhaps it does not represent true transpassive behavior but rather is an artifact.

Effect of Temperature

Figure 7 shows the effect of temperature on the polarization of the metal in 20 percent HCl. Paralleling the effect of concentration, the critical current for passivity increases with increasing temperature. The rate of increase corresponds to an activation energy of about 20 kcal/mol. At 35 C, even at the 20 percent acid concentration, a relatively small current is required to passivate the metal. The dissolution current in the passive range is of very low order of magnitude at all temperatures. Of course, the lower the value of the corrosion current in the passive state, the more stable the passive state.

Effect of Fe^{3+} Additions

Figure 8 shows the effect of FeCl_3 additions on the polarization behavior of Ti-75A in 20 percent HCl at 65 C. FeCl_3 in concentrations of 0.005 M and 0.0005 M accelerates anodic dissolution. A concentration of 0.03 M FeCl_3 reduces the maximum dissolution current slightly. At this concentration cathodic currents are observed in the passive range which indicates a more stable passive potential exists.

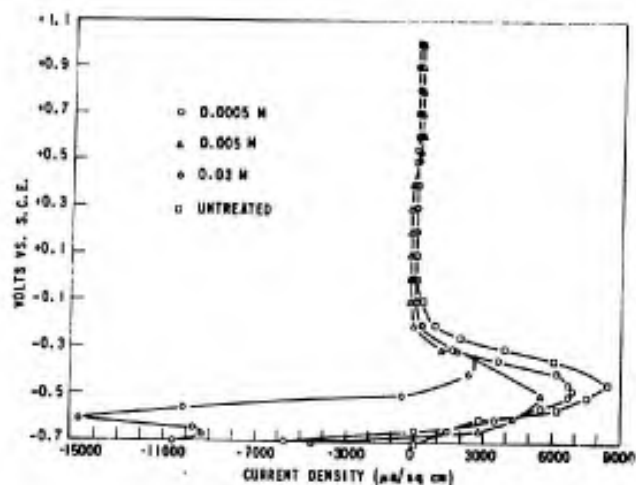


Figure 5. EFFECT OF CuSO_4 CONCENTRATION ON POLARIZATION OF Ti-6Al-6V-2Sn (180 KSI) IN 20% HCl AT 65 C

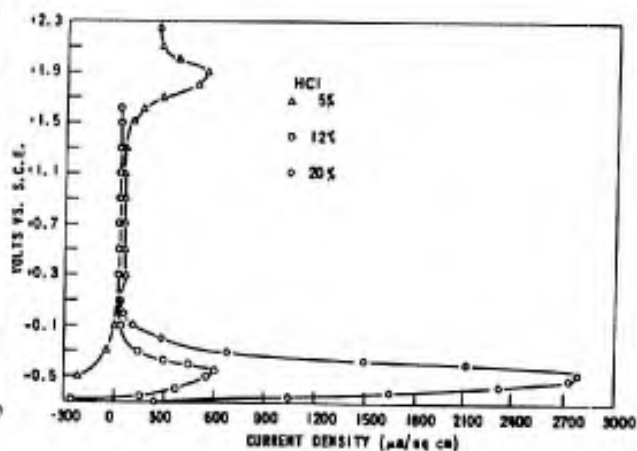


Figure 6. EFFECT OF HCl CONCENTRATION ON POLARIZATION OF COMMERCIAL PURE Ti-75A AT 65 C

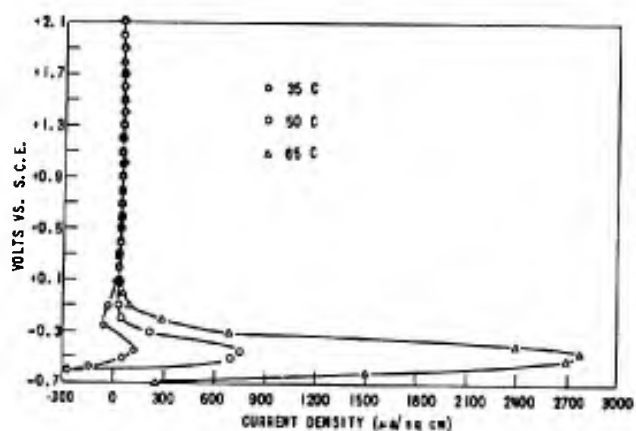


Figure 7. EFFECT OF TEMPERATURE ON POLARIZATION OF COMMERCIAL PURE Ti-75A IN 20% HCl

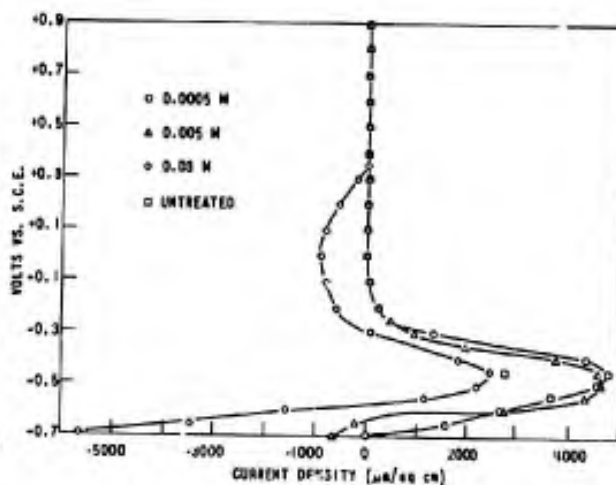


Figure 8. EFFECT OF FeCl_3 CONCENTRATION ON POLARIZATION OF COMMERCIAL PURE Ti-75A IN 20% HCl AT 65 C

Polarization of Ti-8Al-1Mo-1V

Concentration of HCl

Figure 9 shows anodic polarization curves for the alloy as a function of HCl concentration at 65 C. The maximum dissolution current increases with increasing concentration. The critical potential for passivity remains essentially the same. Note the negligible extent of the active region in 5 percent HCl even at 65 C. At potentials between +1.0 v to +1.25 v, depending upon the concentration, a secondary anodic reaction occurred. Such behavior is usually attributed to transpassivity. However, pitting occurred at these potentials indicating that the reaction was not one involving general dissolution or transpassivity.

Effect of Temperature

Figure 10 shows anodic polarization curves for the alloy in 20 percent HCl as a function of temperature. The critical current for passivity increases with increasing temperature at a rate corresponding to an activation energy of about 20 kcal/mol. There is no significant change in the critical potential for passivity. Pitting occurred at all temperatures at potentials above +1.1 v where the current density increased appreciably. The potential at which pitting occurred was temperature dependent.

Effect of Directionality

The anodic behavior of the alloy in both longitudinal and transverse directions in 20 percent HCl and 65 C is shown in Figure 11. The maximum dissolution current density for the specimen fabricated in the transverse direction (machined normal to the working direction) was slightly greater than that fabricated in the longitudinal direction (parallel to the working direction). Pitting occurred in both transverse and longitudinal specimens but at a more noble potential in the longitudinal specimen (+1.3 v versus +0.9 v).

Effect of Heat Treatment

The effect of heat treatment on the polarization of Ti-8Al-1Mo-1V in 20 percent HCl at 65 C is shown in Figure 12. The critical current for passivity and the critical potential for passivity are essentially the same for the alloy in the single- and the duplex-annealed conditions. Localized corrosion (pitting) of the single-annealed alloy occurred at a potential of +1.0 v and of the double-annealed alloy at +1.3 v.

Polarization of Ti-13V-11Cr-3Al

Effect of Concentration of Electrolyte

Figure 13 shows the polarization behavior of the alloy in 5, 12, and 20 percent HCl solutions at 65 C. The critical current for passivity

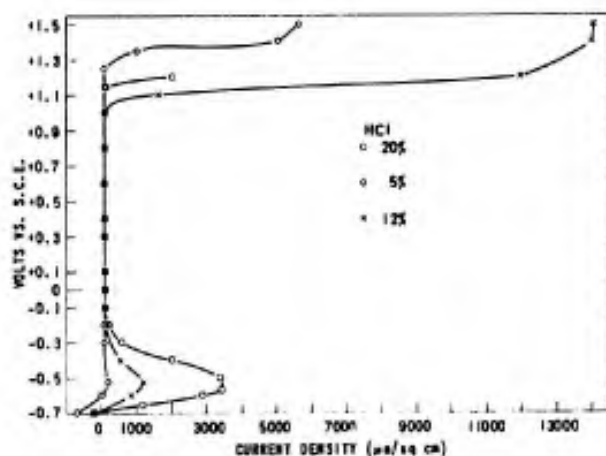


Figure 9. EFFECT OF CONCENTRATION OF HCl ON POLARIZATION OF Ti-8Al-1Mo-1V (DUPLEX ANNEALED) AT 65 C

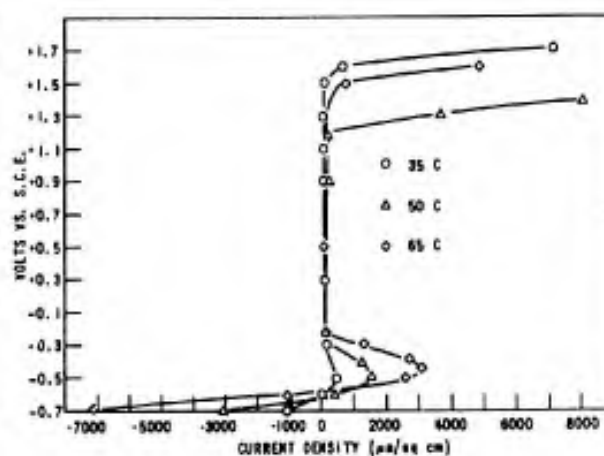


Figure 10. EFFECT OF TEMPERATURE ON POLARIZATION OF Ti-8Al-1Mo-1V (SINGLE ANNEAL, TRANSVERSE) IN 20% HCl

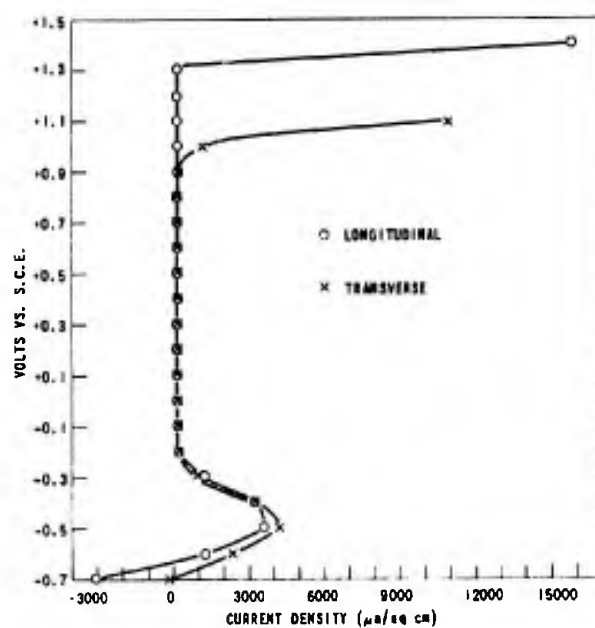


Figure 11. EFFECT OF DIRECTIONALITY ON POLARIZATION OF Ti-8Al-1Mo-1V (DUPLEX ANNEAL) IN 20% HCl AT 65 C

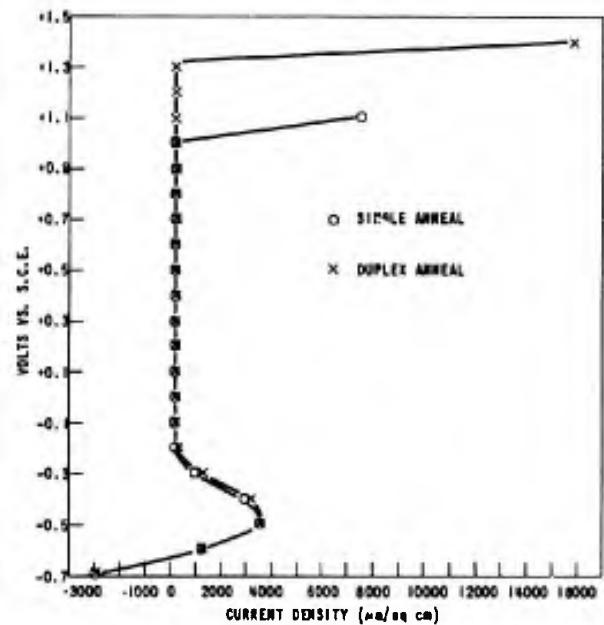


Figure 12. EFFECT OF HEAT TREATMENT ON POLARIZATION OF Ti-8Al-1Mo-1V (LONGITUDINAL) IN 20% HCl AT 65 C

increases with the increasing HCl concentration and the critical potential for passivity shifts in the more noble direction. Although not shown in the figure, above +1.0 v a secondary reaction was observed at all HCl concentrations and was characterized as transpassive behavior due to the 11 percent chromium content of the alloy.

Effect of Temperature

Figure 14 shows that the critical current for passivity increases with increasing temperature. The activation energy for the polarization process (about 20 kcal/mol) is the right order of magnitude for a reaction controlled by chemical reactivity at the surface. The alloy exhibited transpassive behavior at all temperatures at potentials above +1.0 v (not shown).

Effect of Cu^{2+}

Figure 15 shows the effect of CuSO_4 on the polarization of Ti-13V-11Cr-3Al in 20 percent HCl at 65 C. Corrosion is accelerated by the addition of CuSO_4 in concentrations of 0.005 M and 0.0005 M. The anodic reaction is markedly stifled in 0.03 M solution. Note the cathodic currents in the passive range which indicate that the passivity is stable.

Polarization of Ti-6Al-4V

Effect of Temperature

The temperature dependence of the anodic polarization process is shown in Figure 16. The critical current for passivity increases with increasing temperature. Again the activation energy is the right order of magnitude for a chemical-controlled reaction rather than diffusion-controlled. Parallel- ing the effect of temperature, increasing the HCl concentration increased the critical current for passivity.

Comparison of Polarization Behavior of Titanium and Alloys

The anodic behaviors of commercially pure titanium and several alloys in 20 percent HCl at 65 C are compared in Figure 17. Based on maximum dissolution current, alpha-beta Ti-6Al-6V-2Sn shows the least corrosion resistance followed by beta Ti-13V-11Cr-3Al, alpha-beta Ti-6Al-4V, alpha-beta 8Al-1Mo-1V (10% beta), and alpha Ti-75A, in order of increasing corrosion resistance. Since the anodic polarization process was shown to be controlled by reactions occurring at the surface, metal composition and structure should achieve their greatest effect. Composition gradients in a metal create galvanic cells causing accelerated attack of anodic areas. A pure metal or homogeneous single-phase alloy, therefore, is usually more corrosion-resistant than an impure or multiphase alloy, which appears to be the case here. The critical potential for passivity is essentially the same for the metal and the alloys, which means that the alloying does not significantly alter the critical potential for passivity. The commercially pure Ti-75A remains passive throughout the potential range (from -0.2 to +2.3 v). All the alloys exhibit secondary reactions above potentials of +1.0 v. The secondary

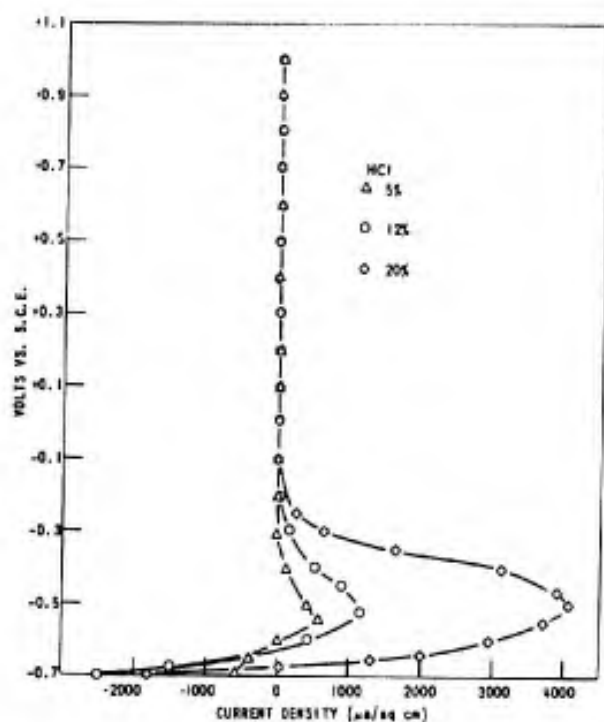


Figure 13. EFFECT OF HCl CONCENTRATION ON POLARIZATION OF Ti-13V-11Cr-3Al AT 65 C

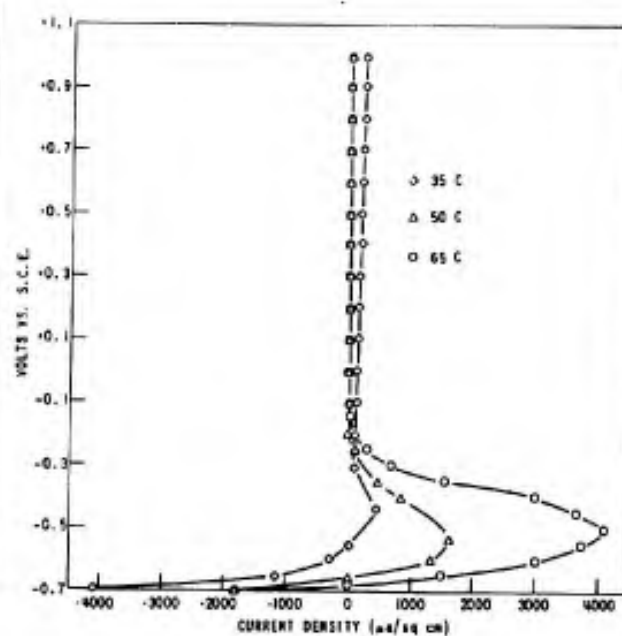


Figure 14. EFFECT OF TEMPERATURE ON POLARIZATION OF Ti-13V-11Cr-3Al IN 20% HCl

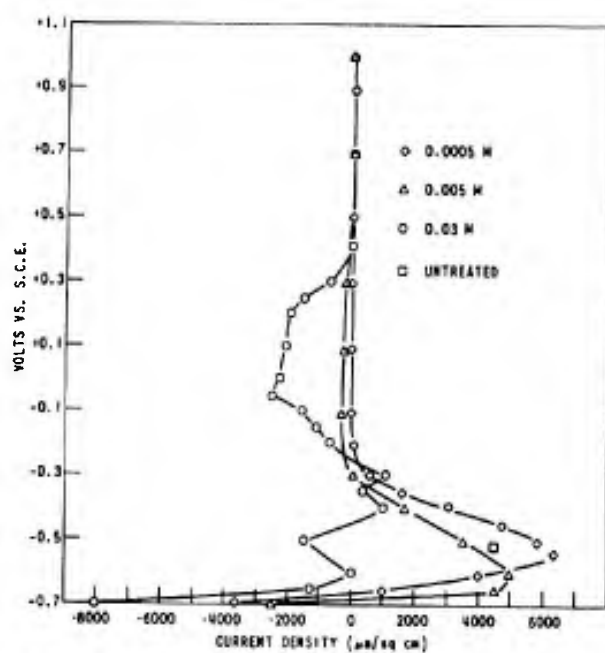


Figure 15. EFFECT OF CuSO_4 CONCENTRATION ON POLARIZATION OF Ti-13V-11Cr-3Al AT 65 C

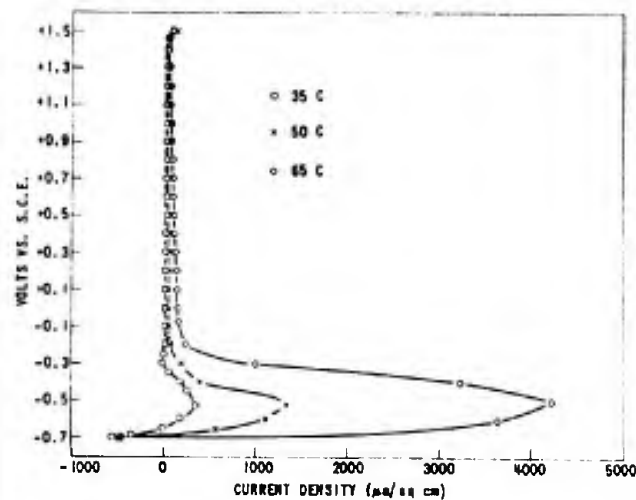


Figure 16. EFFECT OF TEMPERATURE ON POLARIZATION OF Ti-6Al-4V IN 20% HCl

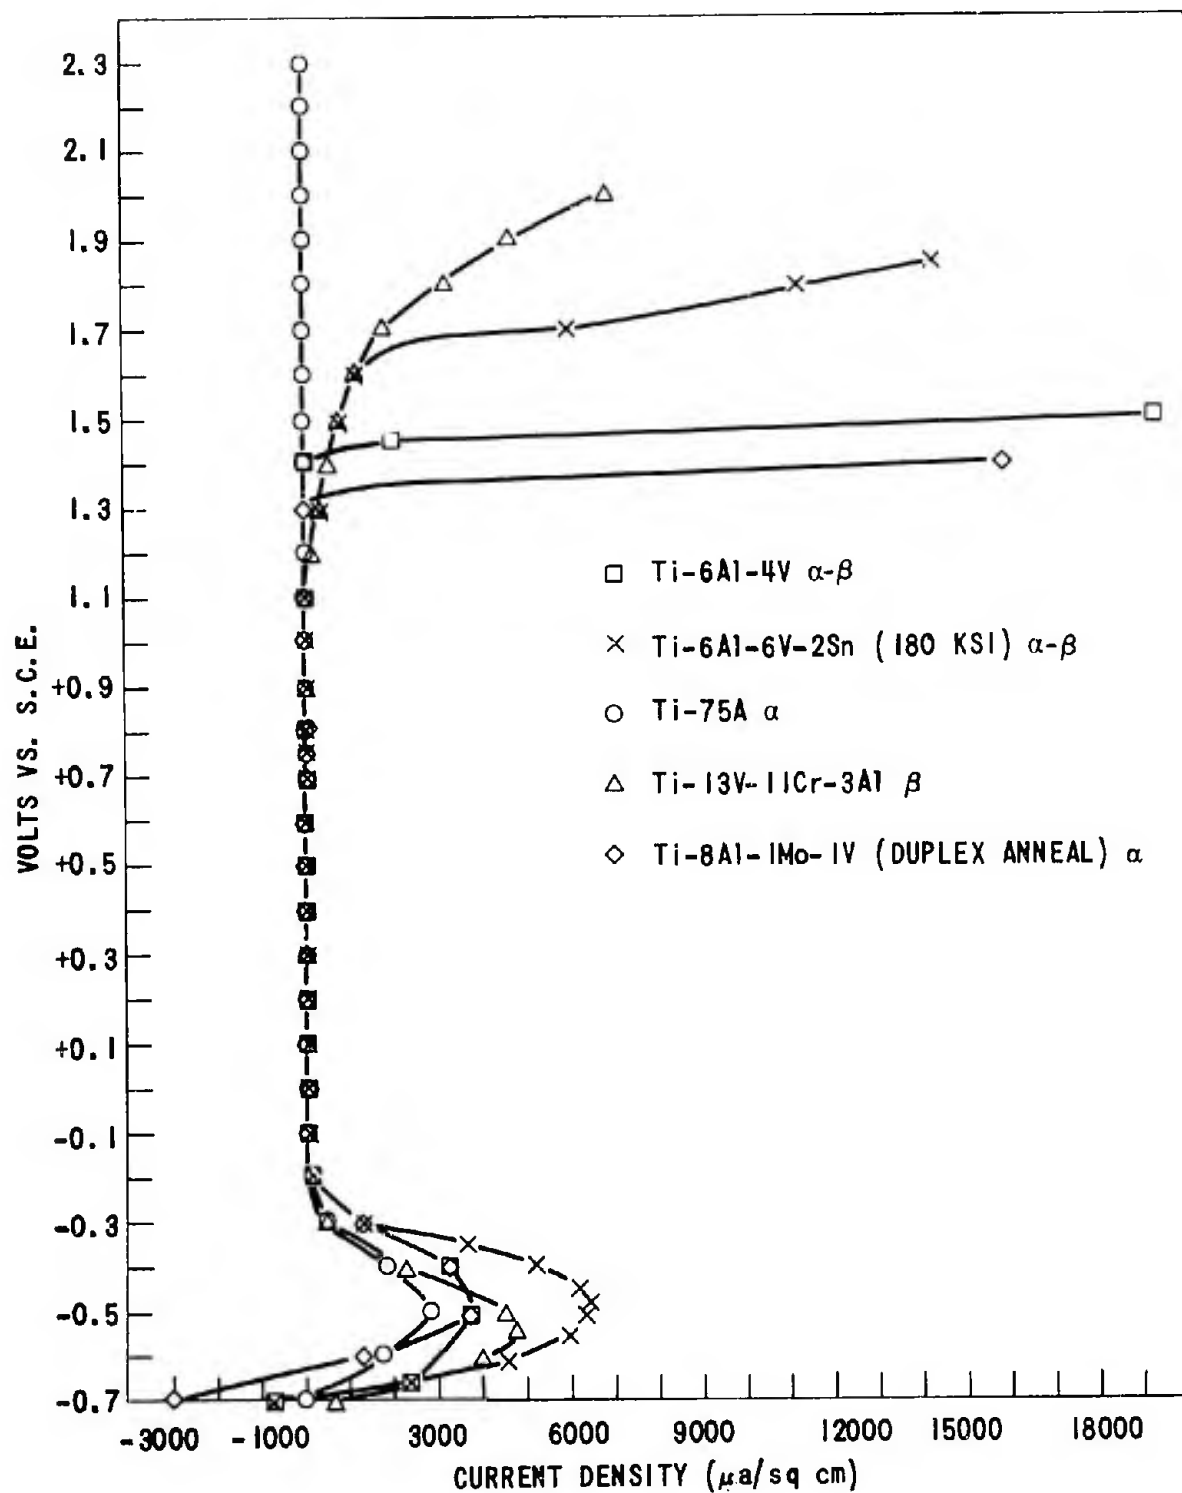


Figure 17. COMPARISON OF POLARIZATION BEHAVIOR OF TITANIUM AND ALLOYS IN 20% HCl AT 65 C

reaction for the Ti-13V-11Cr-3Al alloy (+1.1 v) is attributed to transpassivity. In this region of potential, chromium becomes oxidized to its hexavalent soluble state. The secondary current increase associated with the remaining alloys (Ti-6Al-6V-2Sn, Ti-6Al-4V, Ti-8Al-1Mo-1V) is attributed to localized corrosion or pitting. Comparing the maximum dissolution current densities (i_c) in HCl and H₂SO₄ shown in Table I, it is apparent that dissolution is doubled in HCl. It should be noted here that the pitting observed in HCl solutions was not observed in H₂SO₄ solutions.

Table I. COMPARISON OF MAXIMUM DISSOLUTION CURRENT DENSITIES IN H₂SO₄ AND HCl

Metal	i_c H ₂ SO ₄	i_c HCl
6Al-6V-2Sn(180)	3220	6325
6Al-4V(L)	2170	4255
6Al-4V(T)	2040	3575
8Al-1Mo-1V(DL)	1940	3645
8Al-1Mo-1V(SL)	1910	3580
8Al-1Mo-1V(DT)	1830	4300
8Al-1Mo-1V(ST)	1850	3100
13V-11Cr-3Al	1795	4772
Comm. pure	1430	2863

SUMMARY

Commercially pure titanium and the alloys studied exhibited active-to-passive transitions in HCl. Increasing the acid concentration increased the critical current for passivity and shifted the critical potential for passivity in the noble direction. Increasing the temperature served only to increase the critical current for passivity. Activation energies for the anodic polarization process were the right order of magnitude for a reaction controlled by reactivity at the metal surface. For the alpha-beta alloy 6Al-6V-2Sn the critical current for passivity

increased as the ratio of amounts of beta-to-alpha phase decreased with increasing strength level. The dissolution is accelerated, probably by the galvanic effects and the unfavorable area ratio. Ti-75A, a commercially pure metal, had a smaller critical current for passivity value than did the alloys, which was expected. Secondary current density increases were observed for all the alloys at potentials above +1.0 v. For the 13V-11Cr-3Al alloy such behavior was attributed to transpassivity. For the other alloys the phenomena was attributed to pitting or localized corrosion. The commercially pure metal remained passive in this potential range. The addition of Fe³⁺ and Cu²⁺ (0.03 M) to the HCl facilitated passivation of the metal and its alloys. The maximum dissolution current densities for the metal and alloys in HCl were double those in H₂SO₄. Pitting of several of the alloys occurred in HCl but not in H₂SO₄.

UNCLASSIFIED
Security Classification

DOCUMENT CONTROL DATA - R&D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1 ORIGINATING ACTIVITY (Corporate author) Army Materials and Mechanics Research Center Watertown, Massachusetts 02172		2a REPORT SECURITY CLASSIFICATION Unclassified 2b GROUP
3 REPORT TITLE ANODIC POLARIZATION OF TITANIUM AND ITS ALLOYS IN HYDROCHLORIC ACID		
4 DESCRIPTIVE NOTES (Type of report and inclusive dates)		
5 AUTHOR(S) (Last name, first name, initial) Levy, Milton and Sklover, Gilbert N.		
6. REPORT DATE November 1968	7a. TOTAL NO. OF PAGES	7b. NO. OF REFS 1
8a. CONTRACT OR GRANT NO.	9a. ORIGINATOR'S REPORT NUMBER(S) AMMRC TR 68-22	
b. PROJECT NO. D/A 1C024401A328	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
c. AMCMS Code 5025.11.294		
d. Subtask 38081		
10. AVAILABILITY/LIMITATION NOTICES This document has been approved for public release and sale; its distribution is unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY U. S. Army Materiel Command Washington, D. C. 20315	
13. ABSTRACT Commercially pure titanium and the alloys studied exhibited active to passive transitions in HCl. Increasing the acid concentration increased the critical current for passivity and shifted the critical potential for passivity in the noble direction. Increasing the temperature served only to increase the critical current for passivity. Activation energies for the anodic polarization process were the right order of magnitude for a reaction controlled by reactivity at the metal surface. For the alpha-beta alloy 6Al-6V-2Sn the critical current for passivity increased as the ratio of amounts of beta-to-alpha phase decreased with increasing strength level. The dissolution is accelerated, probably by the galvanic effects and the unfavorable area ratio. Ti-75A, a commercially pure metal, had a smaller critical current for passivity value than did the alloys, which was expected. Secondary current density increases were observed for all the alloys at potentials above +1.0 v. For the 13V-11Cr-3Al alloy such behavior was attributed to transpassivity. For the other alloys the phenomena was attributed to pitting or localized corrosion. The commercially pure metal remained passive in this potential range. The addition of Fe ³⁺ and Cu ²⁺ (0.03 M) to the HCl facilitated passivation of the metal and its alloys. The maximum dissolution current densities for the metal and alloys in HCl were double those in H ₂ SO ₄ . Pitting of several of the alloys occurred in HCl but not in H ₂ SO ₄ . (Authors)		

DD FORM 1 JAN 64 1473

UNCLASSIFIED
Security Classification

UNCLASSIFIED
Security Classification

14 KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Corrosion Inhibition Electrochemistry Electrolytic cells Titanium Physical chemistry						

INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (*either by the originator or by the sponsor*), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through _____."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through _____."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through _____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (*paying for*) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

UNCLASSIFIED
Security Classification