

AD696053

FTD-MT-24-168-69

FOREIGN TECHNOLOGY DIVISION



A STUDY OF THE ELASTIC PROPERTIES OF ORIENTED FIBERGLASS BY THE IMPULSE ACOUSTICAL METHOD

by

Ye. N. Kvasnikov, and A. I. Fotapov



NOV 10 1959

Distribution of this document is unlimited. It may be released to the Clearinghouse, Department of Commerce, for sale to the general public.

Reproduced by the
CLEARINGHOUSE
for Federal Scientific & Technical
Information Springfield Va. 22151

EDITED MACHINE TRANSLATION

A STUDY OF THE ELASTIC PROPERTIES OF ORIENTED FIBERGLASS
BY THE IMPULSE ACOUSTICAL METHOD

By: Ye. N. Kvasnikov, and A. I. Potapov

English pages: 8

SOURCE: AN SSSR. Institut Khimicheskoy Fiziki. Laboratoriya
Armirovannykh Plastikov. Fiziko-Khimiya i Mekhanika
Oriyentirovannykh (Academy of Science, USSR. Institute
of Chemical Physics. Plastics Reinforcement Laboratory).
Izd-vo "Nauka", Moscow, 1967, pp. 172-177.

THIS TRANSLATION IS A REPRODUCTION OF THE ORIGINAL FOREIGN TEXT WITHOUT ANY ANALYTICAL OR EDITORIAL COMMENT. STATEMENTS OR THEORIES ADVOCATED OR IMPLIED ARE THOSE OF THE SOURCE AND DO NOT NECESSARILY REFLECT THE POSITION OR OPINION OF THE FOREIGN TECHNOLOGY DIVISION.	PREPARED BY: TRANSLATION DIVISION FOREIGN TECHNOLOGY DIVISION WP-APR, ONR.
--	---

isapproval of the mater

FOLLOWING ARE THE CORRESPONDING RUSSIAN AND ENGLISH
 DESIGNATIONS OF THE TRIGONOMETRIC FUNCTIONS

Russian	English
sin	sin
cos	cos
tg	tan
ctg	cot
sec	sec
csc	csc
sh	sinh
ch	cosh
th	tanh
cth	coth
sch	sech
csch	csch
arc sin	sin ⁻¹
arc cos	cos ⁻¹
arc tg	tan ⁻¹
arc ctg	cot ⁻¹
arc sec	sec ⁻¹
arc csc	csc ⁻¹
arc sh	sinh ⁻¹
arc ch	cosh ⁻¹
arc th	tanh ⁻¹
arc cth	coth ⁻¹
arc sch	sech ⁻¹
arc csch	csch ⁻¹
rot	curl
lg	log

U. S. BOARD ON GEOGRAPHIC NAMES TRANSLITERATION SYSTEM

Block	Italic	Transliteration	Block	Italic	Transliteration
A	A	A, a	P	P	R, r
B	B	B, b	C	C	S, s
V	V	V, v	T	T	T, t
G	G	G, g	Y	Y	U, u
D	D	D, d	X	X	F, f
E	E	Ye, ye; E, e	K	K	Kh, kh
Ж	Ж	Zh, zh	Ts	Ts	Ts, ts
З	З	Z, z	Ch	Ch	Ch, ch
И	И	I, i	Sh	Sh	Sh, sh
Н	Н	N, n	Shch	Shch	Shch, shch
К	К	K, k	Y	Y	Y, y
Л	Л	L, l	E	E	E, e
М	М	M, m	Yu	Yu	Yu, yu
Н	Н	N, n	Ya	Ya	Ya, ya
О	О	O, o			
П	П	P, p			

• Ye initially, after vowels, and after y, b, c elsewhere.
 When written as W in Russian, transliterate as yu or y.
 The use of diacritical marks is preferred, but such marks
 may be omitted when expediency dictates.

A STUDY OF THE ELASTIC PROPERTIES OF ORIENTED FIBERGLASS BY THE IMPULSE ACOUSTICAL METHOD

Ye. N. Kvasnikov, and A. I. Potapov

Some of the essential mechanical characteristics of fiberglass are the elastic modulus and Poisson's ratio. For determining the elastic characteristics of oriented fiberglass, we used the impulse acoustical method, since it permits revealing the influence of different technological factors and the mode of hardening for mechanical properties of the material.

Elastic properties of oriented fiberglass. Oriented fiberglass belongs to the group of orthogonally-anisotropic materials. Elastic deformations of fiberglass can be described with the aid of Hooke's generalized law. In general, the equations of Hooke's generalized law contain 21 elastic constants. However, inasmuch as constructions made of fiberglass such as pipes, plates, the hulls of ships, constructions used in wall and roof panels and others are subject to plane stress and have an orthotropic structure, then the equations of Hooke's generalized law will have four independent elastic constants in all.

With the aid of the impulse acoustical method, the physical constants of Hooke's generalized law are directly determined [1]:

$$\begin{aligned} \epsilon_{11} &= \nu_1^2 \rho, & (1) \\ \epsilon_{22} &= \nu_2^2 \rho, & (2) \\ \epsilon_{33} &= \nu_3^2 \rho = \nu_1^2 \nu_2^2 \rho, & (3) \end{aligned}$$

where ρ - density; ν_x and ν_y - speed of propagation of longitudinal waves in a plate along the axes of elastic symmetry x and y ; ν_{yx} and ν_{xy} - corresponding propagation speeds of shear waves.

By using formulas (1-3) and the expression of technical elastic constants through the physical [2, 3], the values of Young's modulus E and shear modulus can be obtained:

$$E_x = \rho (\nu_x^2 / \nu_y^2 - \nu_{yx}^2), \quad (4)$$

$$E_y = \rho (\nu_y^2 / \nu_x^2 - \nu_{xy}^2), \quad (5)$$

$$G_{xy} = \rho \nu_{xy}^2. \quad (6)$$

where ν_{12} and ν_{21} - Poisson's ratio, subscripts x and y , as before, pertain to the direction of the axes of elastic symmetry, while C_{11} , C_{22} , C_{66} - physical elastic constants.

For determining the elastic characteristics in rods it is possible to use this expression:

$$\nu = \sqrt{\frac{E}{\rho}}. \quad (7)$$

where ν - speed of elastic waves in the rod; E - Young's modulus, and subscript y indicates direction. This formula is accurate for directions, which coincide with the axes of elastic symmetry. In the first approximation dependence (7) can also be accepted for other directions.

By equating the values of elastic modulus obtained by the speed of propagation of waves in a plate (4) and (5), to the corresponding values calculated by the speed of propagation of waves in a rod (7), one can determine ν_{12} and ν_{21} :

$$v_{11} = \sqrt{\frac{E_1}{\rho_1}} \quad (8)$$

$$v_{22} = \sqrt{\frac{E_2}{\rho_2}} \quad (9)$$

where v_0 and v_{90} - speeds of longitudinal waves in a rod along axes x and y .

For determination of E_0 there is no need to cut rods in directions which differ from the basic, and it is possible to use the known formulas of the theory of elasticity of an anisotropic body [2, 3]. By applying the previously deduced expressions (7) and (8), we will obtain:

$$E_0 = \frac{v_0^2 (\rho_0^2 v_0^2 - \rho_1^2)}{v_0^2 v_1^2 + v_2^2 v_3^2 + v_4^2 v_5^2} \quad (10)$$

$$\lambda = \frac{v_0^2}{v_1^2} \cdot b = \frac{v_0^2 (\rho_0^2 v_0^2 - \rho_1^2)}{v_2^2} - \frac{1}{1 + \frac{1}{b}}$$

where

here v_{45} - speed of longitudinal waves in a rod, cut at an angle of 45° to the direction of the fibers.

Below, on the basis of experimental data, it will be shown that for determining the speed at any angle to the direction of fibers both in a plate and in a rod this formula is applicable:

$$v_0 = \frac{v_1 v_2 v_3}{v_1 v_2 + v_2 v_3 + v_3 v_1} \quad (11)$$

$$\lambda = v_0 v_1 \cdot b_1 = v_0 v_2 \cdot (b + 1) \lambda_1$$

where

here v_0 , v_{45} , v_{90} - speed of propagation of elastic waves either in a rod or in a plate at angles of 0° , 45° and 90° to the direction of the fibers.

Formula (11) is empirical and was taken by analogy with the theoretical equation.

Experimental investigations. As the object of investigation the anisotropic fiberglass material SVAM was selected, the physical and mechanical properties of which have been sufficiently completely and widely discussed in literature [4]. For investigating the elastic characteristics by the impulse acoustical method [5, 6] SVAM material made by the Leningrad laminated plastics plant was used. The characteristics of these materials are given in Table 1.

Table 1. Characteristics of sheet fiberglass SVAM adhesive - epoxy-phenol resin.

Sheet number	Dimensions, mm	Density, g/cm ³	Content of fibers, %		
			fiberglass	radical and	transverse fibers
2-1	500x200x4.0	2.08	78	11	11
3-10	500x200x4.0	2.04	72	11	11
3-3	500x200x4.0	2.07	77	11	11

All fiberglass of the sheets were marked and sonicated in accordance with the layout shown in Fig. 1. As an emitter of ultrasonic waves the Polish ultrasonic instrument Betonoskop was used, as well as elastic wave converters on a frequency of 40 kHz. As a result of sonification the speed of propagation of elastic waves in a plate of fiberglass in the directions shown in Fig. 1 was determined; after that, from each sheet at angles of 0° , 15° , 30° , 45° , 60° , 75° and 90° to the direction of fibers from 4 to 5 samples each were cut. The length of the samples was from 200 to 400 mm, the width was 20 mm, and the thickness corresponded to the thickness of sheets shown in Table 1. All of the samples were sonified to determine the speed of elastic waves in the rods by the layout shown in Fig. 2. The values of speeds in the plate and in the rods were compared with the values of speeds calculated by formula (11).

Along with measurements of elastic properties, mechanical tests were conducted of material by the acoustical method for determining the value of elastic constants in accordance with All-Union State

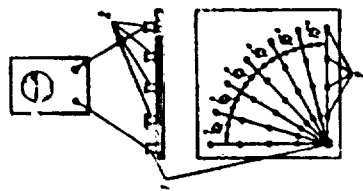


Fig. 1. Location diagram of the emitter (1) and the receivers (2) during surface sonification of a plate made of fiberglass.




Fig. 2. Diagram of through sonification of fiberglass samples. 1 - ultrasonic instrument. 2 - emitter. 3 - sample. 4 - receiver.

Standard 9550-60. The very same samples were subjected to the mechanical tests on which the dynamic elastic characteristics were determined by the acoustical method.

As a result of the tests Young's moduli were determined in directions of 0°, 15°, 30°, 45°, 60°, 75° and 90° to the direction of fibers in the fiberglass. All measured and calculated data are given in Table 2.

These data show that the dynamic elastic characteristics noticeably differ from the static, where this difference is increased with a change of angle between the direction of sonification and the axis of elastic symmetry, reaching a maximum value for the direction with minimum elastic modulus. The dependence of the elastic modulus on the

Let us note that for the first two sheets, the axes of symmetry coincided with the directions 0°, 90° and 45°, and for the last one only with two - 0° and 90°.

Table 2. Results of determining the elastic characteristics of SVAM oriented fiberglass by the impulse acoustical method.

Direction of fibers in a plate	Type of sonification				Dynamic elastic modulus, kg/cm^2	Static elastic modulus, kg/cm^2	Conversion factor, μ
	(I) - through	(II) - through	(III) - through	(IV) - through			
0	4130	4130	4130	4130	3030	3120	0.79
15	4130	4130	4130	4130	3030	3120	0.79
30	4130	4130	4130	4130	3030	3120	0.79
45	4130	4130	4130	4130	3030	3120	0.79
60	4130	4130	4130	4130	3030	3120	0.79
75	4130	4130	4130	4130	3030	3120	0.79
90	4130	4130	4130	4130	3030	3120	0.79

Note. Values of constants were calculated by formulas (4), (5), (7), (8), (10) and (12) in this article.

rate of application contradicts its physical sense. This dependence is explained by the fact that in fiberglass, along with elastic deformations, highly elastic deformations are also developed. When testing by the impulse method, samples of fiberglass experience minute stresses at extraordinarily high rates of load application; therefore, the fiberglass does not "succeed" in manifesting nonelastic properties.

For converting from the elastic characteristics determined by the acoustical method to the characteristics obtained in the standard tests, it is possible to use conversion factors. Determination of these factors was made by comparing the dynamic elastic characteristics with the elastic characteristics defined by the All-Union State Standard. The results of this comparison are given in Table 2, where the conversion factors were obtained in the following way:

$$K_{\text{trans}} = \frac{E_{\text{trans}}/E_{\text{std}}}{K_{\text{std}}} = \frac{K_1}{\sqrt{1 + \frac{1}{2} \frac{K_2}{K_1} + \frac{1}{4} \frac{K_3}{K_1}}}, \quad (12)$$

$$\text{where } K_1 = \frac{E_{\text{std}}}{K_{\text{std}}}, \quad K_2 = K_1/K_{45}, \quad K_3 = (K_1 + 1)/4.$$

In conclusion, it is possible to note that the impulse acoustical method permits reliably determining the elastic characteristics of fiberglass.

The investigations conducted showed that acoustical parameters and dynamic elastic constants of orthotropic fiberglass are described with sufficient accuracy by tensor formulas of the theory of elasticity of an anisotropic body. For converting from dynamic elastic characteristics to standard, conversion factors were obtained which consider the pressure of nonelastic deformations in a polymeric adhesive.

Bibliography

1. K. S. Aleksandrov. Trudy In-ta lesa i drevesiny, 1, 51 (1962).
2. A. L. Rabinovich. Trudy TsAGI, No. 582 (1946).
3. S. G. Lekhnitskiy. Teoriya uprugosti anizotropnogo tela (Theory of elasticity of an anisotropic body). M., Gostekhizdat, 1950.
4. Ye. K. Ashkenazi. Anizotropiya mekhanicheskikh svoystv nekotorykh stekloplastikov (Anisotropy of mechanical properties of certain fiberglasses). Leningradskiy dom nauchno-tekhnicheskoy propagandy, 1961; A. K. Burov, G. D. Andreevskaya. Steklovoloknistyye anizotropnyye materialy i ikh tekhnicheskoye primeneniye (Fiberglass anisotropic materials and their technical application). M., Izd-vo AN SSSR, 1956.
5. I. A. Krylov. Elektronno-akusticheskiy i radiometricheskii

metody ispytaniya materialov (Electronic-acoustical and radiometric methods of materials testing). M., Gosstroyizdat, 1963.

6. V. G. Firstov, S. K. Kashkin. Nerazrushayushchiye metody ispytaniya dorozhnykh konstruktiv i materialov (Nondestructive methods of testing road constructions and materials). M., Soyuzacrizdat, 1964.

DATA HANDLING PAGE									
SI-ACCESSION NO. SI-DOCUMENT LOC		SI-TOPIC TASS							
779501310		glass reinforced plastic, elastic modulus, elastic wave, acoustic analysis, shear modulus, Young modulus, glass property							
SI-TITLE A STUDY OF THE ELASTIC PROPERTIES OF ORIENTED FIBERGLASS BY THE IMPULSE ACOUSTICAL METHOD									
SI-SUBJECT AREA									
11, 20									
SI-AUTHOR CO-AUTHORS		KVASNIKOV, YE. N.; 16-POTAPOV, A. I.							
SI-SOURCE AN SSR. INSTITUT KHMICHESKOY FIZIKI. LABORATORIYA ARMIROVANNYKH PLASTIKOV. FIZIKO-KHIMIYA I MEKHANIKA OPIVENTIROVANNYKH STEKLO-PLASTIKOV. MOSCOW. IZL. NO "DANKA" (RUSSIAN)		FTD-MT-24-168-69							
SI-SECURITY AND DOWNGRADING INFORMATION		72302-78							
UNCL. O		UNCL. O							
SI-REF. FRAME NO		SI-SUPPLEMENT		SI-CHARACTER		SI-GEOMETRICAL DATA		SI-REVISION	
1889 4113				UR		8			
CONTRACT NO.		SI-REF. ACC. NO.		PUBLICATION DATE		TRANSLATION		MCME	
		65-A701874		94-					
STEP NO.		02-UR/0000/67/000/000/0172/0177							
ABSTRACT									
(U) The impulse acoustical method was used to determine the elastic properties of SVAM oriented glass reinforced plastics. Formulas were given for Young's modulus, shear modulus, and Poisson's ratio. These constants were related to the density of the material and the speed of elastic wave propagation in the material. An equation was given for the speed of elastic wave propagation in any direction as a function of the angle and speed of propagation relative to the fiber direction. Experimental values of the elastic constants were obtained in three SVAM materials having an epoxy phenol resin binder, densities ranging from 2.01 to 2.08 g/cm³ (superscript 3), glass fiber contents ranging from 72 to 78 wt percent, and ratios of longitudinal to transverse fibers of 1 to 1 ratio and 1 to 5 ratio. A schematic diagram showed the experimental arrangement of ultrasonic generator, receiver, and sample. The speed of elastic wave propagation was measured in samples at angles of 0, 15, 30, 45, 60, 75, and 90 degrees to the fiber direction. Samples were 200 to 400 mm long, 20 mm wide, and 4.9 to 5.3 mm thick. Mechanical testing was done to determine values of the elastic constants for comparison with the impulse acoustical method. Experimental results were given for the modulus of elasticity as determined by static and dynamic methods.									

APC 4888

(SI-REF. ACC. NO.)

FTD-MT-24-168-69

DISTRIBUTION LIST

Mr. Cys.	Organization	Mr. Cys.
	OTHER DOD AGENCIES	

2	Hq USAF	20	DDC
1	ACIC (ACDEL-7)	1	C072 CDC INLAND COMBAT
2	AFCLR (CLXLR)	1	C013 Pictinny Area
1	ARL (ARB) WP, AF	1	C023 Harry Diamond Lab
1	ETAC (NAC)	1	C025 Aberdeen IF
1	Hq AFSC	1	C035 Aviation Mat Com
1	AFETR (ETW)	1	C019 MID Redstone
1	AFWL (MIF)	1	D153 Pac Natl Range
9	AGD (ASLR)	1	H300 USAIC
1	ESD (ES/ESDT)		
1	SAMSO (SMFA)		
1	FTD		
3	TDLAE		
	AID (2)		
	PHS (1)		
10	TDBAS-2		
1	TDB D-2		
1	TDBR		
1	TDBS		
8	TDPQ (PHE)		
	PEG (1)		
	PEH (1)		
	PEK (1)		
	PF (4)		
	PH (1)		
1	TDPTAM		
1	TDPTN/V		

OTHER GOVERNMENT AGENCIES

AEC (Ten.)	2
AFG (Wash)	2
NAFEC	1
NASA (ATSS-T)	1

DISTRIBUTION TO BE MADE BY

DIA (DIACO-3)	23
B124 DIAS-1 Data Base	
B167 DIAS-2D	
B177 DIAP-10A	
B168 OACSI-USAIC	
DOD U.S. Navy (ST.C)	
D220 GTR	
P055 CIA/OCR/CD (.)	
1090 NSA (CREF/CDB) (6)	