

050602

D6-24471

November 1969


---

EFFECT OF QUENCHING RATE  
ON  
STRESS-CORROSION CRACK GROWTH RATES  
IN  
2024-T4 ALUMINUM

---

By

M.V. Hyatt

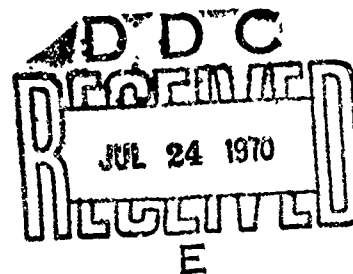

**BOEING** COMMERCIAL AIRPLANE GROUP

Renton, Washington

Sponsored by  
Advanced Research Projects Agency  
ARPA Order No. 878

Reproduced by the  
CLEARINGHOUSE  
for Federal Scientific & Technical  
Information Springfield Va. 22151

This document has been approved for public release and sale; its distribution is unlimited.

EFFECT OF QUENCHING RATE ON STRESS-CORROSION  
CRACK GROWTH RATES IN 2024-T4 ALUMINUM

M.V. Hyatt

ABSTRACT

Stress-corrosion crack growth rates in double cantilever beam specimens of 2024-T4 aluminum quenched at two rates from the solution-treatment temperature were compared. The specimens quenched at the slower rate had the faster crack growth rate. This finding agrees with data from other studies in which intergranular corrosion susceptibility was determined by measuring percent loss in tensile strength of preexposed sheet tension specimens.

INTRODUCTION

When quenched at slow rates, 2024-T4 is prone to intergranular attack and may be susceptible to stress-corrosion cracking and exfoliation. Work performed by L. A. Willey using the interrupted-quench technique (1) established the temperature range during quenching in which the corrosion characteristics are established. The most critical changes in both corrosion characteristics and tensile properties were found to occur in the 750° to 550°F temperature range during quenching.

Willey (1) and Lifka and Sprowles (2) have measured the effects of quenching rate between 750° and 550°F on tensile properties and resistance to corrosion of 2024-T4 and 7075-T6 sheet specimens. Stressed (to 75% of yield strength) and unstressed sheet tension specimens of these two alloys that had been quenched at different rates were exposed to alternate immersion in 3.5% NaCl solution for 12 weeks. The specimens were then pulled to failure and the percentage loss in tensile strength for the various specimens determined. These data are presented in Fig. 1, along with the type of corrosion attack observed at the different quench rates. Studies by Mears, Brown, and Dix (3) and Hunter, Frank, and Robinson (4) explain this behavior based on localized electrochemical effects associated with the formation of grain boundary precipitates and adjacent depleted zone.

---

The author is associated with the Commercial Airplane Group,  
The Boeing Company, Renton, Washington.

The goal of the present study was to measure the effect of quench rate on actual stress-corrosion crack growth rates rather than on strength losses of preexposed tension specimens.

#### MATERIALS AND TEST PROCEDURES

Double cantilever beam (DCB) specimens of the configuration shown in Fig.-2 were used for this study. The advantages and use of this specimen in studying stress-corrosion cracking in high-strength aluminum alloys have been described by the author (5,6,7,8,9,10). By using this specimen and Eq. (1) (from Ref. 7), stress-corrosion crack growth rate data can be obtained as a function of plane-strain stress intensity  $K_I$ .

$$K_I = \frac{vEh [3h (a + 0.6h)^2 + h^3]^{1/2}}{4 [(a + 0.6h)^3 + h^2a]} \quad (1)$$

where:  $v$  = total deflection of the two arms of the DCB specimen at the load point (centerline of loading bolt).  
 $E$  = modulus of elasticity ( $10.3 \times 10^6$  for aluminum alloys)  
 $h$  = 1/2 specimen height  
 $a$  = crack length measured from load point (centerline of loading bolt)

The procedure for obtaining the crack growth rate data is illustrated schematically in Fig. 3. The loading bolt is turned until a sharp crack is popped in from the end of the machined notch. Plane-strain fracture toughness  $K_{Ic}$  can be calculated from Eq. (1) by measuring  $v$  and  $a$  at any subsequent pop-in. After the crack has been advanced a few tenths of an inch by several pop-ins, the bolt is left fixed, giving a constant crack opening displacement (COD), and the 3.5% NaCl environment is applied. Under these conditions the load  $P$  at the bolt and  $K_I$  at the crack tip decrease as the stress-corrosion crack length increases (Figs. 3b and 3c). The slope of the resulting crack

length-time curve in Fig. 3a then gives the crack growth rate as a function of  $K_I$ . As the crack length  $a$  increases and  $K_I$  decreases, a  $K_I$  level may eventually be reached below which growth ceases or is negligible. This  $K_I$  level, designated  $K_{Isc}$ , is shown in Fig. 3c. Use of this technique is especially suited to aluminum alloys with elongated grain structures, since stress-corrosion cracking is intergranular and cracks are kept in plane by the elongated grain structure of the material.

For this study two DCB specimens were machined from 1-in.-thick 2024-T351 plate. The specimens were re-solution treated, quenched into either cold water (75°F) or water at 150°F, and naturally aged to the T4 temper. Average quenching rates between 750° and 550°F were calculated from Fig. 14 in Ref. 2 to be 330°F/sec and 80°F/sec for the two quenching conditions.

Both specimens were bolt loaded to  $K_{Ic}$  and the steel bolts were insulated by masking the bolt end of the specimens with a vinyl coating. The specimens were then placed upright (bolt end up) and, using a polyethylene squeeze bottle, several drops of an aqueous solution of 3.5% NaCl were placed in the machined notch of the specimens. The NaCl solution was applied three times each working day at 4-hr intervals. Crack lengths were monitored using a hand lens and ruler.

## RESULTS AND DISCUSSION

The stress-corrosion crack growth rates for the two specimens are shown in Fig. 4. The more slowly quenched specimen shows a growth rate 1.6 to 4 times faster than that for the more rapidly quenched specimen at equivalent  $K_I$  levels.

Previous work (9) has shown that quenched-in residual stresses in re-heat-treated DCB blanks such as were used in this study cause errors in  $K_I$  calculations based on Eq. (1). The errors result from geometry changes in the arms of the DCB specimens as the stress-corrosion crack propagates through the specimen. Residual compressive stresses on the surfaces of the specimen cause the two arms to bow apart slightly as the crack grows and relieves the residual tensile stresses inside the

specimen. This effectively increases the COD at the crack tip and makes  $K_I$  higher than calculated with Eq. (1). Thus, the  $K_I$ -rate ( $K_I$  versus crack growth rate) curves for these specimens with residual quenching stresses should be moved to the right in Fig. 4. However, the curve for the cold-water-quenched specimen should be shifted further to the right, since that specimen has the higher residual quenching stresses and therefore the greater error in calculated  $K_I$ . Shifting the curves in Fig. 4 as described would only increase their separation. Therefore, despite the residual stress problem with these re-heat-treated and quenched DCB specimens, it can be concluded from Fig. 4 that stress-corrosion crack growth rates for 2024-T4 increase with decreasing quench rate. The mechanism for the increased crack growth rate is most certainly the same as that found responsible for increased susceptibility to intergranular attack and increased loss in tensile strength of 2024-T4 aluminum after preexposure, namely, the precipitation of copper-rich phases along grain boundaries during slow quenching with subsequent depletion of copper adjacent to grain boundaries (3). This gives rise to a difference in solution potential between the two areas, creating an anodic path in the copper-depleted regions adjacent to the boundary.

#### CONCLUSIONS


Slow quenching rates for 2024-T4 increase susceptibility to intergranular attack and increase the growth rate of actual stress-corrosion cracks.

#### ACKNOWLEDGMENTS

The author would like to thank J. O. LaMotte for his help in gathering the stress-corrosion crack growth data and D. E. Piper for his comments on the manuscript. This work sponsored by the Advanced Research Projects Agency of the Department of Defense, ARPA Order No. 878, under Contract No. N00014-66-C0365.

#### REFERENCES

1. E. H. Dix, Jr., "Thermal Treatment of Aluminum Alloys," Physical Metallurgy of Aluminum Alloys, American Society for Metals, 1949, pp. 200-240
2. H. Y. Hunsicker, "The Metallurgy of Heat Treatment," Aluminum, Vol. I: Properties, Physical Metallurgy, and Phase Diagrams, edited by K. R. Van Horn, American Society for Metals, 1967, pp. 109-162
3. R. B. Mears, R. H. Brown, and E. H. Dix, Jr., "A Generalized Theory of the Stress Corrosion of Alloys," Symposium on Stress-Corrosion Cracking of Alloys, ASTM-AIME, 1945
4. M. S. Hunter, G. R. Frank, Jr., and D. L. Robinson, "Mechanism of Corrosion of 2024 Alloy as Revealed by Electron Microscopy," Proceedings of Second International Congress on Metallic Corrosion, National Association of Corrosion Engineers, 1963
5. J. C. McMillan and M. V. Hyatt, Development of High-Strength Aluminum Alloys With Improved Stress-Corrosion Resistance, Technical Report AFML-TR-148, June 1968
6. NRL Memorandum Report 1941, Seventh Quarterly Report, ARPA Coupling Program on Stress-Corrosion Cracking, October 1968
7. M. V. Hyatt, Use of Precracked Specimens in Stress-Corrosion Testing of High-Strength Aluminum Alloys, D6-24466, The Boeing Company, November 1969
8. M. V. Hyatt, Use of Precracked Specimens in Selecting Heat Treatments for Stress-Corrosion Resistance in High-Strength Aluminum Alloys, D6-24467, The Boeing Company, November 1969
9. M. V. Hyatt, Effects of Residual Stresses on Stress-Corrosion Crack Growth Rates in Aluminum Alloys, D6-24469, The Boeing Company, November 1969
10. M. V. Hyatt, Effects of Specimen Geometry and Grain Structure on Stress-Corrosion Cracking Behavior of Aluminum Alloys, D6-24470, The Boeing Company, November 1969

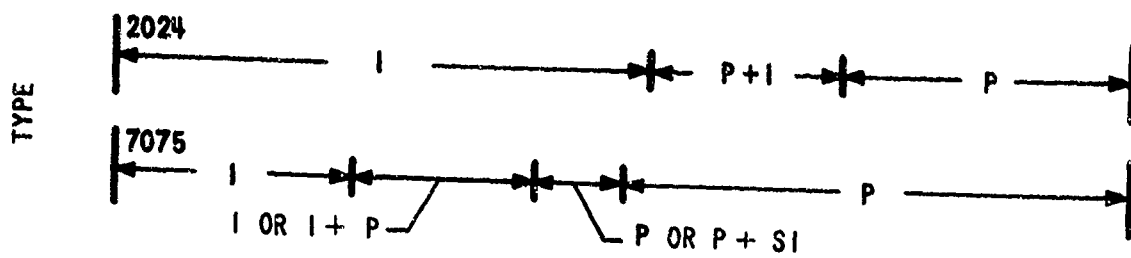

CORROSION: I = INTERGRANULAR, P = PITTING, SI = SLIGHT INTERGRANULAR


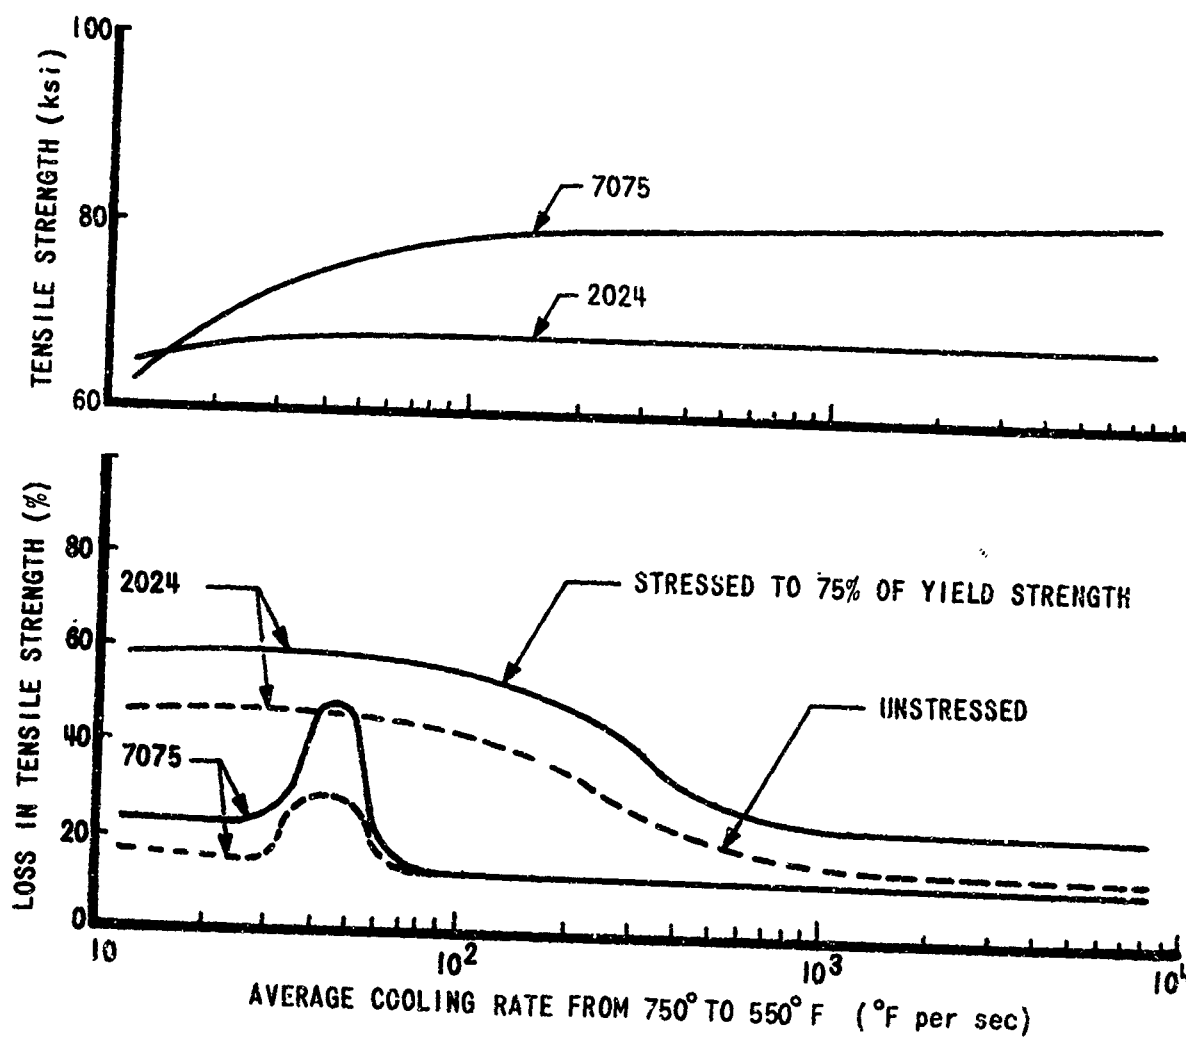


Figure 1 Effects of quenching rate on tensile properties and corrosion resistance of 2024-T4 and 7075-T6 sheet. Stressed and unstressed specimens were exposed to alternate immersion in 3.5% NaCl solution for 12 weeks before testing (from Ref. 2).

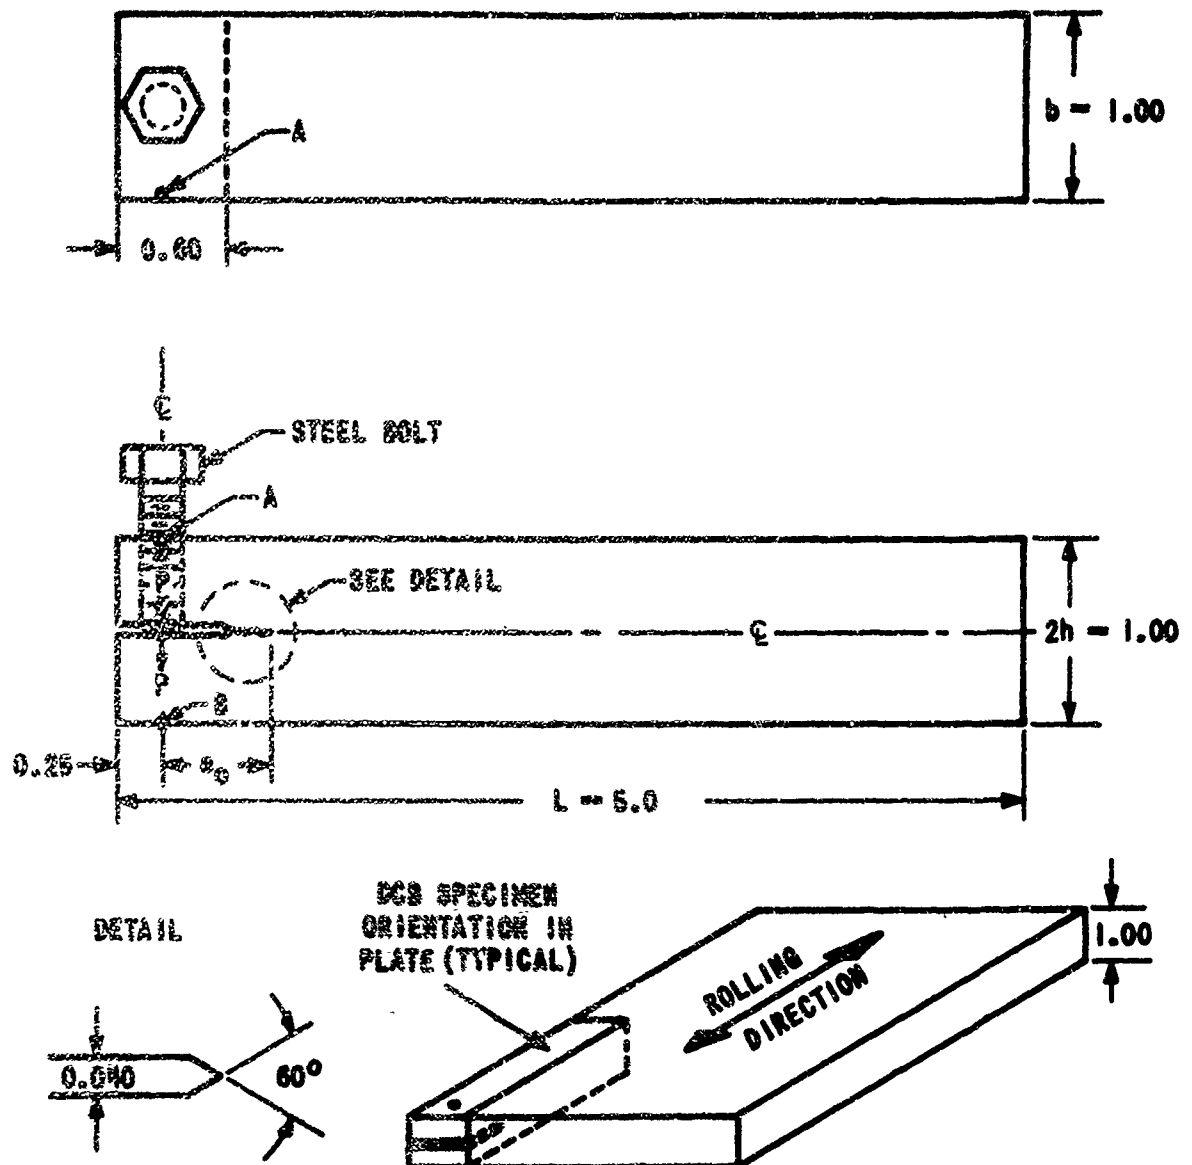

CRACK OPENING DISPLACEMENT  $v$  EQUALS THE MEASURED DEFLECTION BETWEEN POINTS A AND B ALONG THE BOLT CENTERLINE

**Figure 2** Double cantilever beam specimen used for stress-corrosion testing of high-strength aluminum alloys.

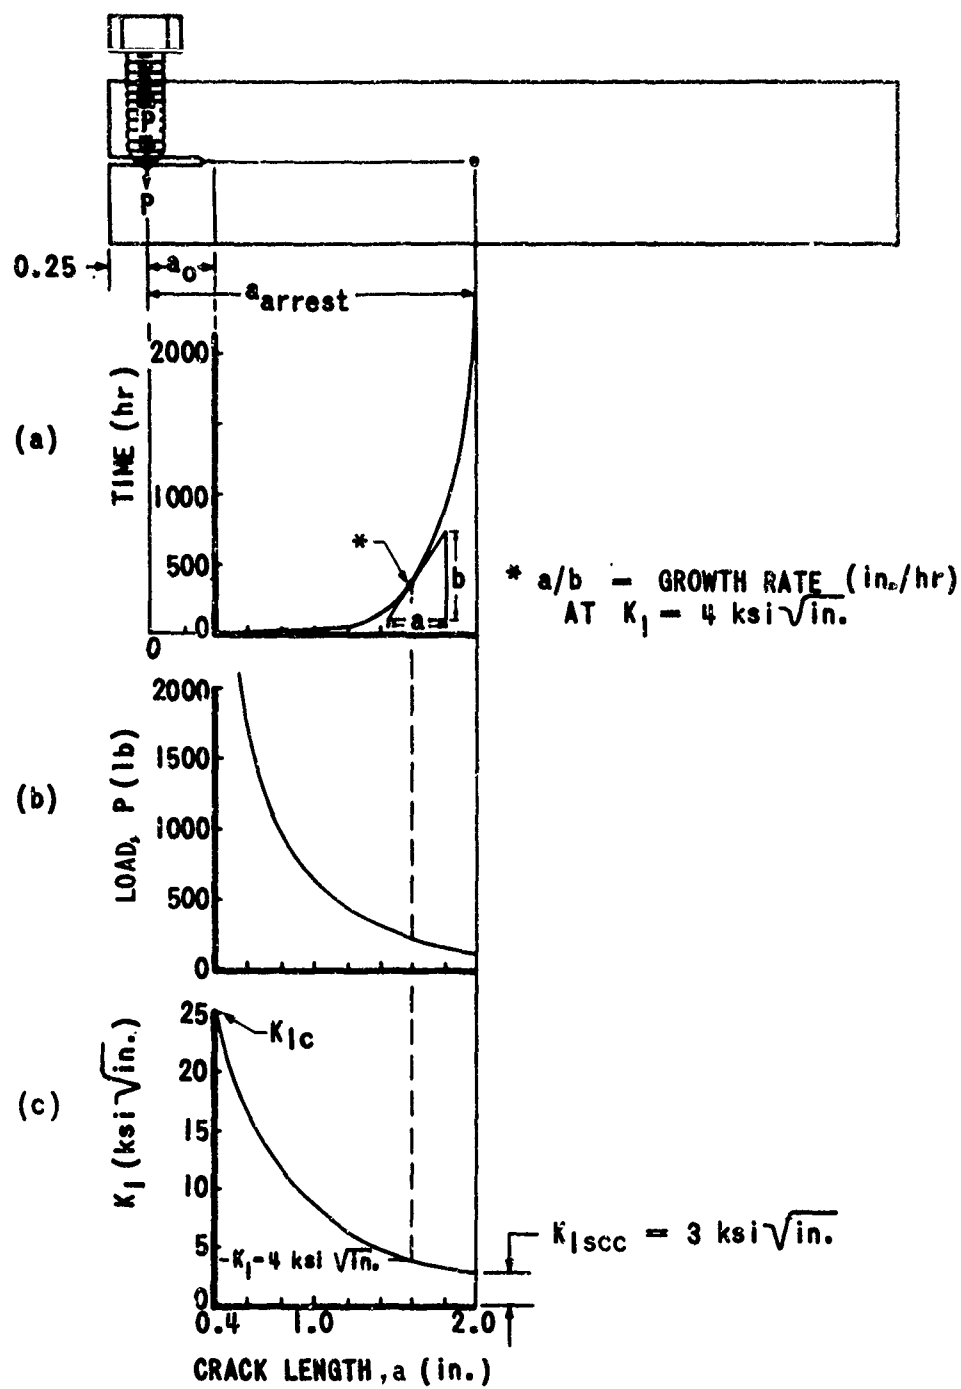


Figure 3 Effect of crack growth on load and stress intensity under constant crack opening displacement conditions ( $v = 0.010$  in.) in a 1- by 1- by 5- in. aluminum-alloy DCB specimen.

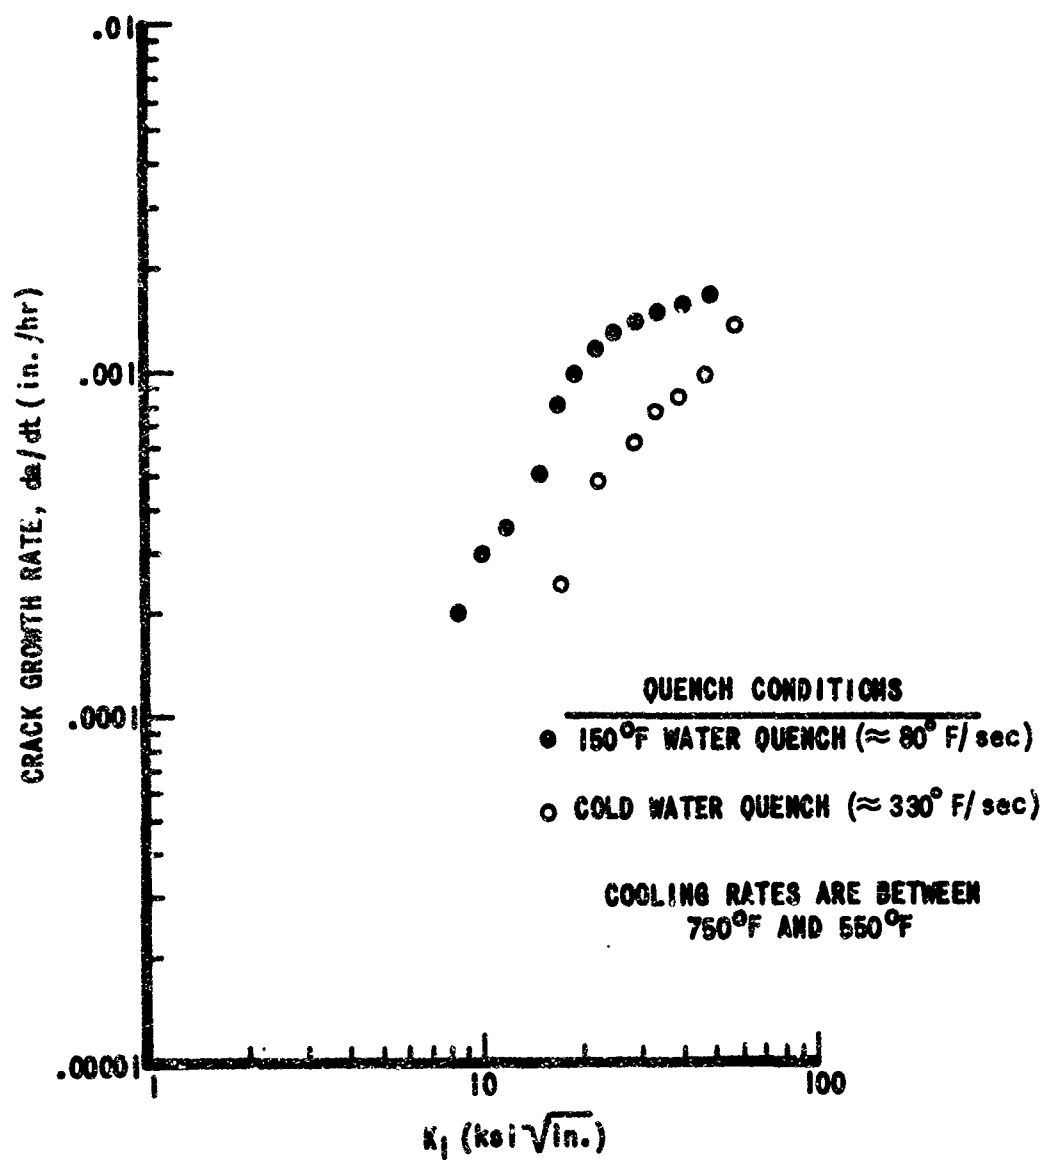


Figure 4 Effect of quenching rate on  $K_I$ -rate data for reheat-treated 2024-T4 DCB specimens from 1-in.-thick plate.

Unclassified

Security Classification

| DOCUMENT CONTROL DATA - R & D                                                                                                                                                                                                                                                                                                                                                                                                                                               |                                                                                |                                                             |
|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------|-------------------------------------------------------------|
| (Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)                                                                                                                                                                                                                                                                                                                                          |                                                                                |                                                             |
| 1. ORIGINATING ACTIVITY (Corporate author)                                                                                                                                                                                                                                                                                                                                                                                                                                  |                                                                                | 2a. REPORT SECURITY CLASSIFICATION                          |
| The Boeing Company<br>Commercial Airplane Group<br>Renton, Washington                                                                                                                                                                                                                                                                                                                                                                                                       |                                                                                | Unclassified                                                |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                             |                                                                                | 2b. GROUP                                                   |
| 3. REPORT TITLE                                                                                                                                                                                                                                                                                                                                                                                                                                                             |                                                                                |                                                             |
| Effect of Quenching Rate on Stress-Corrosion Crack Growth Rates<br>in 2024-T <sub>3</sub> Aluminum                                                                                                                                                                                                                                                                                                                                                                          |                                                                                |                                                             |
| 4. DESCRIPTIVE NOTES (Type of report and inclusive dates)                                                                                                                                                                                                                                                                                                                                                                                                                   |                                                                                |                                                             |
| Research Report                                                                                                                                                                                                                                                                                                                                                                                                                                                             |                                                                                |                                                             |
| 5. AUTHOR(S) (First name, middle initial, last name)                                                                                                                                                                                                                                                                                                                                                                                                                        |                                                                                |                                                             |
| Michael V. Hyatt                                                                                                                                                                                                                                                                                                                                                                                                                                                            |                                                                                |                                                             |
| 6. REPORT DATE                                                                                                                                                                                                                                                                                                                                                                                                                                                              | 7a. TOTAL NO. OF PAGES                                                         | 7b. NO. OF REFS                                             |
| November 1969                                                                                                                                                                                                                                                                                                                                                                                                                                                               | 9                                                                              | 4                                                           |
| 8a. CONTRACT OR GRANT NO.                                                                                                                                                                                                                                                                                                                                                                                                                                                   | 9a. ORIGINATOR'S REPORT NUMBER(S)                                              |                                                             |
| DDO014-66-00365 (ARPA Order 878)                                                                                                                                                                                                                                                                                                                                                                                                                                            |                                                                                |                                                             |
| 9. PROJECT NO.                                                                                                                                                                                                                                                                                                                                                                                                                                                              | 9b. OTHER REPORT NO(S) (Any other numbers that may be assigned<br>this report) |                                                             |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                             | Boeing Document D6-24471                                                       |                                                             |
| 10. DISTRIBUTION STATEMENT                                                                                                                                                                                                                                                                                                                                                                                                                                                  |                                                                                |                                                             |
| This document has been approved for public release and sale;<br>its distribution is unlimited                                                                                                                                                                                                                                                                                                                                                                               |                                                                                |                                                             |
| 11. SUPPLEMENTARY NOTES                                                                                                                                                                                                                                                                                                                                                                                                                                                     |                                                                                | 12. SPONSORING MILITARY ACTIVITY                            |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                             |                                                                                | Advanced Research Projects Agency,<br>Department of Defense |
| 13. ABSTRACT                                                                                                                                                                                                                                                                                                                                                                                                                                                                |                                                                                |                                                             |
| <p>Stress-corrosion crack growth rates in double cantilever beam specimens of 2024-T<sub>3</sub> aluminum quenched at two rates from the solution-treatment temperature were compared. The specimens quenched at the slower rate had the faster crack growth rate. This finding agrees with data from other studies in which intergranular corrosion susceptibility was determined by measuring percent loss in tensile strength of preexposed sheet tension specimens.</p> |                                                                                |                                                             |

DD FORM 1473  
1 NOV 65

Unclassified  
Security Classification

| 12.<br>KEY WORDS                                                                                                                                         | LINK A |    | LINK B |    | LINK C |    |
|----------------------------------------------------------------------------------------------------------------------------------------------------------|--------|----|--------|----|--------|----|
|                                                                                                                                                          | ROLE   | WT | ROLE   | WT | ROLE   | WT |
| Aluminum Alloy 2024-T3<br>Stress-Corrosion Cracking<br>Crack Growth Rate<br>Stress Intensity Factor<br>Double Cantilever Beam Specimen<br>Quenching Rate |        |    |        |    |        |    |