

AD-751 864

ROTARY SWAGED RAPID-FIRE GUN BARRELS

D. C. Drennen. et al

Battelle Memorial Institute

Prepared for:

Army Weapons Command

August 1972

DISTRIBUTED BY:

NTIS

National Technical Information Service
U. S. DEPARTMENT OF COMMERCE
5285 Port Royal Road, Springfield Va. 22151


AD751864

AD

SWERR-TR-72-56

ROTARY SWAGED RAPID-FIRE GUN BARREL

August 1972

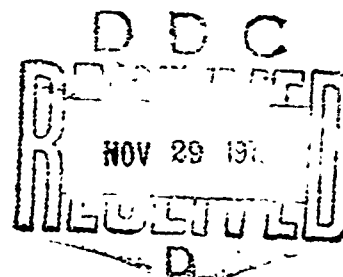

TECHNICAL REPORT

D. C. Drennen, Dr. C. M. Jackson
Battelle Memorial Institute

and

R. B. Miclot, Dr. K. R. Iyer
USAWECOM

RESEARCH DIRECTORATE

Reproduced by
NATIONAL TECHNICAL
INFORMATION SERVICE
U S Department of Commerce
Springfield VA 22151

WEAPONS LABORATORY USAWECOM

RESEARCH, DEVELOPMENT AND ENGINEERING DIRECTORATE

Details of illustrations in
this document may be better
studied on microfiche

U. S. ARMY WEAPONS COMMAND

Approved for public release, distribution unlimited.

DISPOSITION INSTRUCTIONS:

Destroy this report when it is no longer needed. Do not return it to the originator.

DISCLAIMER:

The findings of this report are not to be construed as and official Department of the Army position unless so designated by other authorized documents.

The citation of commercial products in this report does not constitute an official indorsement or approval of such products.

1		2		3	
4		5		6	
7		8		9	
10		11		12	
13		14		15	
16		17		18	
19		20		21	
22		23		24	
25		26		27	
28		29		30	
31		32		33	
34		35		36	
37		38		39	
40		41		42	
43		44		45	
46		47		48	
49		50		51	
52		53		54	
55		56		57	
58		59		60	
61		62		63	
64		65		66	
67		68		69	
70		71		72	
73		74		75	
76		77		78	
79		80		81	
82		83		84	
85		86		87	
88		89		90	
91		92		93	
94		95		96	
97		98		99	
100		101		102	
103		104		105	
106		107		108	
109		110		111	
112		113		114	
115		116		117	
118		119		120	
121		122		123	
124		125		126	
127		128		129	
130		131		132	
133		134		135	
136		137		138	
139		140		141	
142		143		144	
145		146		147	
148		149		150	
151		152		153	
154		155		156	
157		158		159	
160		161		162	
163		164		165	
166		167		168	
169		170		171	
172		173		174	
175		176		177	
178		179		180	
181		182		183	
184		185		186	
187		188		189	
190		191		192	
193		194		195	
196		197		198	
199		200		201	
202		203		204	
205		206		207	
208		209		210	
211		212		213	
214		215		216	
217		218		219	
220		221		222	
223		224		225	
226		227		228	
229		230		231	
232		233		234	
235		236		237	
238		239		240	
241		242		243	
244		245		246	
247		248		249	
250		251		252	
253		254		255	
256		257		258	
259		260		261	
262		263		264	
265		266		267	
268		269		270	
271		272		273	
274		275		276	
277		278		279	
280		281		282	
283		284		285	
286		287		288	
289		290		291	
292		293		294	
295		296		297	
298		299		300	
301		302		303	
304		305		306	
307		308		309	
310		311		312	
313		314		315	
316		317		318	
319		320		321	
322		323		324	
325		326		327	
328		329		330	
331		332		333	
334		335		336	
337		338		339	
340		341		342	
343		344		345	
346		347		348	
349		350		351	
352		353		354	
355		356		357	
358		359		360	
361		362		363	
364		365		366	
367		368		369	
370		371		372	
373		374		375	
376		377		378	
379		380		381	
382		383		384	
385		386		387	
388		389		390	
391		392		393	
394		395		396	
397		398		399	
400		401		402	
403		404		405	
406		407		408	
409		410		411	
412		413		414	
415		416		417	
418		419		420	
421		422		423	
424		425		426	
427		428		429	
430		431		432	
433		434		435	
436		437		438	
439		440		441	
442		443		444	
445		446		447	
448		449		450	
451		452		453	
454		455		456	
457		458		459	
460		461		462	
463		464		465	
466		467		468	
469		470		471	
472		473		474	
475		476		477	
478		479		480	
481		482		483	
484		485		486	
487		488		489	
490		491		492	
493		494		495	
496		497		498	
499		500		501	
502		503		504	
505		506		507	
508		509		510	
511		512		513	
514		515		516	
517		518		519	
520		521		522	
523		524		525	
526		527		528	
529		530		531	
532		533		534	
535		536		537	
538		539		540	
541		542		543	
544		545		546	
547		548		549	
550		551		552	
553		554		555	
556		557		558	
559		560		561	
562		563		564	
565		566		567	
568		569		570	
571		572		573	
574		575		576	
577		578		579	
580		581		582	
583		584		585	
586		587		588	
589		590		591	
592		593		594	
595		596		597	
598		599		600	
601		602		603	
604		605		606	
607		608		609	
610		611		612	
613		614		615	
616		617		618	
619		620		621	
622		623		624	
625		626		627	
628		629		630	
631		632		633	
634		635		636	
637		638		639	
640		641		642	
643		644		645	
646		647		648	
649		650		651	
652		653		654	
655		656		657	
658		659		660	
661		662		663	
664		665		666	
667		668		669	
670		671		672	
673		674		675	
676		677		678	
679		680		681	
682		683		684	
685		686		687	
688		689		690	
691		692		693	
694		695		696	
697		698		699	
700		701		702	
703		704		705	
706		707		708	
709		710		711	
712		713		714	
715		716		717	
718		719		720	
721		722		723	
724		725		726	
727		728		729	
730		731		732	
733		734		735	
736		737		738	
739		740		741	
742		743		744	
745		746		747	
748		749		750	
751		752		753	
754		755		756	
757		758		759	
760		761		762	
763		764		765	
766		767		768	
769		770		771	
772		773		774	
775		776		777	
778		779		780	
781		782		783	
784		785		786	
787		788		789	
790		791		792	
793		794		795	
796		797		798	
799		800		801	
802		803		804	
805		806		807	
808		809		810	
811		812		813	
814		815		816	
817		818		819	
820		821		822	
823		824		825	
826		827		828	
829		830		831	
832		833		834	
835		836		837	
838		839		840	
841		842		843	
844		845		846	
847		848		849	
850		851		852	
853		854		855	
856		857		858	
859		860		861	
862		863		864	
865		866		867	
868		869		870	
871		872		873	
874		875		876	
877		878		879	
880		881		882	
883		884		885	
886		887		888	
889		890		891	
892		893		894	
895		896		897	
898		899		900	
901		902		903	
904		905		906	
907		908		909	
910		911		912	
913		914		915	
916		917		918	
919		920		921	
922		923		924	
925		926		927	
928		929		930	
931		932		933	
934		935		936	
937		938		939	
940		941		942	
943		944		945	
946		947		948	
949		950		951	
952		953		954	
955		956		957	
958		959		960	
961		962		963	
964		965		966	
967		968		969	
970		971		972	
973		974		975	
976		977		978	
979		980		981	
982		983		984	
985		986		987	
988		989		990	

Unclassified

Security Classification

DOCUMENT CONTROL DATA - R & D		
(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)		
1. ORIGINATING ACTIVITY (Corporate author) U.S. Army Weapons Command Res., Dev. & Eng. Dir. Rock Island, Ill 61201		2a. REPORT SECURITY CLASSIFICATION Unclassified 2b. GROUP Columbus, Ohio 43201
3. REPORT TITLE ROTARY SWAGED RAPID-FIRE GUN BARRELS (U)		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates)		
5. AUTHOR(S) (First name, middle initial, last name) D. C. Drennen, C.M. Jackson - Battelle Memorial Institute R. B. Miclot and K. R. Iyer - USAWECOM		
6. REPORT DATE August 1972	7a. TOTAL NO. OF PAGES 87	7b. NO. OF REFS 9
8a. CONTRACT OR GRANT NO. DAAf03-70-C-0005 b. PROJECT NO. DA 1W562604A607 c. AMS Code 5524.11.80700.03 d.	8b. ORIGINATOR'S REPORT NUMBER(S) SWERR-TR-72-56 9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
10. DISTRIBUTION STATEMENT Approved for public release, distribution unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY U. S. Army Weapons Command	
13. ABSTRACT A program was undertaken by the Research Directorate, Weapons Laboratory USAWECOM, to investigate the feasibility of forming 7.62mm rifled gun barrels from three high-temperature alloys and a stainless steel by swaging. The high-temperature superalloys selected for evaluation were Inconel 718, Udimet 700, and Crucible CG-27, whereas the stainless steel was Armco 21-6-9. Gun barrel blanks of each alloy were prepared by gun drilling. Twenty-two rifled 7.62mm gun barrel blanks of the four selected materials were formed by swaging without any insolvable problems. Evaluation of the as-swaged blanks revealed that high quality gun barrels can be formed from each of these alloys. Further analyses, conducted on short samples of the swaged barrel blanks, showed that the age-hardenable alloys can be heat treated without destroying the bore configuration. As-swaged barrel blanks of Inconel 718 and Udimet 700 were heat treated and 7.62mm M60 barrels were fabricated from these blanks. These completed barrels and the nonheat-treatable Armco 21-6-9 were test fired, metallurgically analyzed, and their performance characteristics were documented. The performance characteristics of Crucible CG-27, as a rapid-fire small caliber gun barrel, will be presented in a separate technical report. (U) (Drennen, D.C., Jackson, C.M., Miclot, R.B., and Iyer, K. R.)		

DD FORM 1473
1 NOV 65REPLACES DD FORM 1473, 1 JAN 64, WHICH IS
OBSOLETE FOR ARMY USE.

Unclassified

Security Classification

AD

RESEARCH DIRECTORATE
WEAPONS LABORATORY USAWECOM
RESEARCH, DEVELOPMENT AND ENGINEERING DIRECTORATE
U. S. ARMY WEAPONS COMMAND

TECHNICAL REPORT
SWERR-TR-72-56

ROTARY SWAGED RAPID-FIRE GUN BARRELS

D. C. Drennen, Dr. C. M. Jackson
Battelle Memorial Institute

and

R. B. Miclot, Dr. K. R. Iyer
USAWECOM

August 1972

Details of illustrations in
this document may be better
studied on microfiche

DA 1W562604A607

AMS Code 5524.11.80700.03

Approved for public release, distribution unlimited.

ABSTRACT

A program was undertaken by the Research Directorate, Weapons Laboratory USAWECOM, to investigate the feasibility of forming 7.62mm rifled gun barrels from three high-temperature alloys and a stainless steel by swaging. The high-temperature superalloys selected for evaluation were Inconel 718, Udimet 700, and Crucible CG-27, whereas the stainless steel was Armco 21-6-9.

Gun barrel blanks of each alloy were prepared by gun drilling. Twenty-two rifled 7.62mm gun barrel blanks of the four selected materials were formed by swaging without any insolvable problems. Evaluation of the as-swaged blanks revealed that high quality gun barrels can be formed from each of these alloys. Further analyses, conducted on short samples of the swaged barrel blanks, showed that the age-hardenable alloys can be heat treated without destroying the bore configuration.

As-swaged barrel blanks of Inconel 718 and Udimet 700 were heat treated and 7.62mm M60 barrels were fabricated from these blanks. These completed barrels and the nonheat-treatable Armco 21-6-9 were test fired, metallurgically analyzed, and their performance characteristics were documented. The performance characteristics of Crucible CG-27, as a rapid-fire small caliber gun barrel, will be presented in a separate technical report.

FOREWORD

The swaging studies and swaging of blanks made of superalloys for this program were performed by Battelle Memorial Institute, Columbus, Ohio, under Contract DAAF03-70-C-0005. The contract supervisor was R. B. Miclot. The test firings of the rotary-swaged barrels and the test-firing analysis were conducted by R. B. Miclot and Dr. K. R. Iyer of the Research Directorate, Weapons Laboratory USAWECOM.

CONTENTS

	<u>Page</u>
TITLE PAGE	i
ABSTRACT	ii
FOREWORD	iii
TABLE OF CONTENTS	iv
TABULAR DATA	vi
ILLUSTRATIONS	vii
INTRODUCTION	1
LITERATURE SEARCH AND FIELD SURVEY	1
EXPERIMENTAL WORK	5
Materials	5
Preliminary Cold-Swaging Trials	5
Preparation of Gun Barrel Blanks	8
Heat Treatment of Crucible Alloy CG-27 Blanks	8
Evaluation of Gun Barrel Blanks	11
Machinability	11
Surface Finish	11
Metallographic Studies	12
Hardness Studies	15
Cold Swaging of Gun Barrel Blanks	15
Equipment and Tooling	17
Procedure	20
Results and Discussion	22

CONTENTS

	<u>Page</u>
Evaluation of Swaged Blanks	24
Nondestructive Testing	24
Metallographic Examination of As-Swaged Samples of Gun Barrel Blanks	26
Metallographic Examination of Heat- Treated Samples of Gun Barrel Blanks	32
Bore Dimensions	38
Hardness Studies	44
Test Firing and Analysis of Rotary-Swaged Barrels	52
CONCLUSIONS	68
LITERATURE CITED	69
APPENDIX A - Data Sheets for the Cold Swaging of Gun Barrel Blanks	70
APPENDIX B - Diameter and Straightness Data Cold-Swaged Gun Barrel Blanks	74
DISTRIBUTION	82
DD FORM 1473 Document Control Data - R&D	86

TABULAR DATA

<u>Table</u>		<u>Page</u>
I	Certified Chemical Composition of Alloys	6
II	Specified Heat Treatment of Alloys for Cold-Swaging Trials	7
III	Hardness of Samples of Crucible Alloy CG-27 Heat Treated at 1900°F	10
IV	Hardness of Transverse Sections of Gun Barrel Blanks	16
V	Surface Finish of Bore of Gun Barrel Blanks	25
VI	Quality Rating of Experimental 7.62mm Gun Blanks	27
VII	Heat Treatments for Age-Hardenable Selected Gun Barrel Materials	32
VIII	Heat Treatments used for Transverse Samples of Gun Barrel Blanks	34
IX	Bore Dimensions of Gun Barrel Blanks	43
X	Vickers Hardness of Transverse Sections of As-Swaged Gun Barrel Blanks	50
XI	Summary of Knoop Microhardness Data on Gun Barrel Blank Samples in the As-Swaged Condition and After Heat Treatment	51
XII	Identification and Quality Rating of Experimental 7.62mm Gun Barrel Blanks	53
XIII	Gun Barrel Service Life - Firing Schedule I	55
XIV	Gun Barrel Service Life - Firing Schedule II	55

ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	Interior Configuration, 7.62mm Gun Barrel	2
2	High-Temperature Yield Strengths of Selected Gun Barrel Materials Compared to Cr-Mo-V Steel	3
3	Gun Barrel Blank	9
4	Transverse Sections of Gun Barrel Blanks	13
5	Multiflow Machine During Cold Swaging of Gun Barrel Blanks	18
6	Dies used to Cold Swage Gun Barrels in Multiflow Machine	19
7	Carbide Rifling Mandrel used to Form Bore Contour of Gun Barrels During Cold Swaging	21
8	Gun Barrel Blanks Formed by Cold Swaging	23
9	As-Swaged Inconel 718	28
10	As-Swaged Armco 21-6-9	29
11	As-Swaged Udimet 700	30
12	As-Swaged Crucible Alloy CG-27	31
13	Heat-Treated Inconel 718	35
14	Heat-Treated Udimet 700	36
15	Heat-Treated Crucible Alloy CG-27	37
16	Transverse Section of Heat-Treated Inconel Alloy 718 Gun Barrel Sample 126	39
17	Transverse Section of Heat-Treated Udimet 700 Gun Barrel Sample 376	40
18	Transverse Section of Heat-Treated Crucible Alloy CG-27 Gun Barrel Sample 452	41

ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
19	Transverse Section of As-Swaged Armco 21-6-9 Gun Barrel Sample 226	42
20	Knoop Hardness of Inconel 718 Gun Barrel Sample 126	45
21	Knoop Hardness of Armco 21-6-9 Gun Barrel Sample 226	47
22	Knoop Hardness of Udimet 700 Gun Barrel Sample 376	48
23	Knoop Hardness of CG-27 Gun Barrel Sample 452	49
24	Longitudinal Section of Bore of Test- Fired Armco 21-6-9 Gun Barrel	57
25	Transverse Section of Bore of Test- Fired Armco 21-6-9 Gun Barrel	58
26	Replicate of Bore of Test-Fired Inconel 718 Gun Barrel	59
27	Replicate of Bore of Test-Fired Udimet 700 Gun Barrel	60
28	Transverse Section of Bore 2 Inches from Chamber of Test-Fired Inconel 718 Gun Barrel, Firing Schedule I	61
29	Transverse Section of Bore 1 Inch from Muzzle End of Test-Fired Inconel 718 Gun Barrel, Firing Schedule I	62
30	Transverse Section of Bore 1 Inch from Muzzle End of Test-Fired Inconel 718 Gun Barrel, Firing Schedule II	63
31	Transverse Section of Bore 2 Inches from Chamber of Test-Fired Udimet 700 Gun Barrel, Firing Schedule I	64

ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
32	Transverse Section of Bore 1-1/2 Inches from Chamber of Test-Fired Udimet 700 Gun Barrel, Firing Schedule I	65
33	Transverse Section of Bore 1 Inch from Muzzle End of Test-Fired Udimet 700 Gun Barrel, Firing Schedule I	66
34	Transverse Section of Bore 1 Inch from Muzzle End of Test-Fired Udimet 700 Gun Barrel, Firing Schedule II	67

INTRODUCTION

Currently, U.S. small-arms gun barrels are produced from Cr-Mo-V low alloy steels with nominally 0.48 per cent carbon, heat treated to a hardness of Rockwell C 32-34. The bore is chromium plated, and may contain a liner of Stellite 21 in the breech end.

The Research Directorate of the Weapons Laboratory USAWECOM is concerned with the improvement of the performance of small-arms gun barrel materials. Therefore, a program was undertaken with the Columbus Laboratories of Battelle Memorial Institute to study procedures suitable for manufacturing gun barrels from high-strength materials. Specifically, the objective of this program is to investigate the feasibility of forming rifled gun barrels from the following three high-temperature alloys and a stainless steel by swaging techniques:

<u>Alloy</u>	<u>Alloy Base</u>
Inconel Alloy 718	Nickel
Udimet Alloy U 700	Nickel
Crucible Alloy CG-27	Iron
Armco Alloy 21-6-9	Iron

The barrel to be formed is a 7.62mm gun barrel and the interior configuration is shown in Figure 1.

The typical short-time, high-temperature yield strengths of the alloys selected for evaluation as gun barrel materials are shown in Figure 2. The principal objection to using materials such as these for gun barrels, aside from the inherently higher cost than that of alloy steel, is that their machinability and formability are relatively low. Consequently, the applicability of the rotary swage to the rifling of gun barrel bores to offset cost disadvantages was investigated.

LITERATURE SEARCH AND FIELD SURVEY

The technical literature concerning the internal swaging of gun barrels was examined. A very limited amount of information was found on (1) the design of, and materials for, dies and mandrels, (2) the starting blank configuration, (3) reductions in area required, (4) feeding methods for the workpiece, and (5) lubricants used during the forming operation.


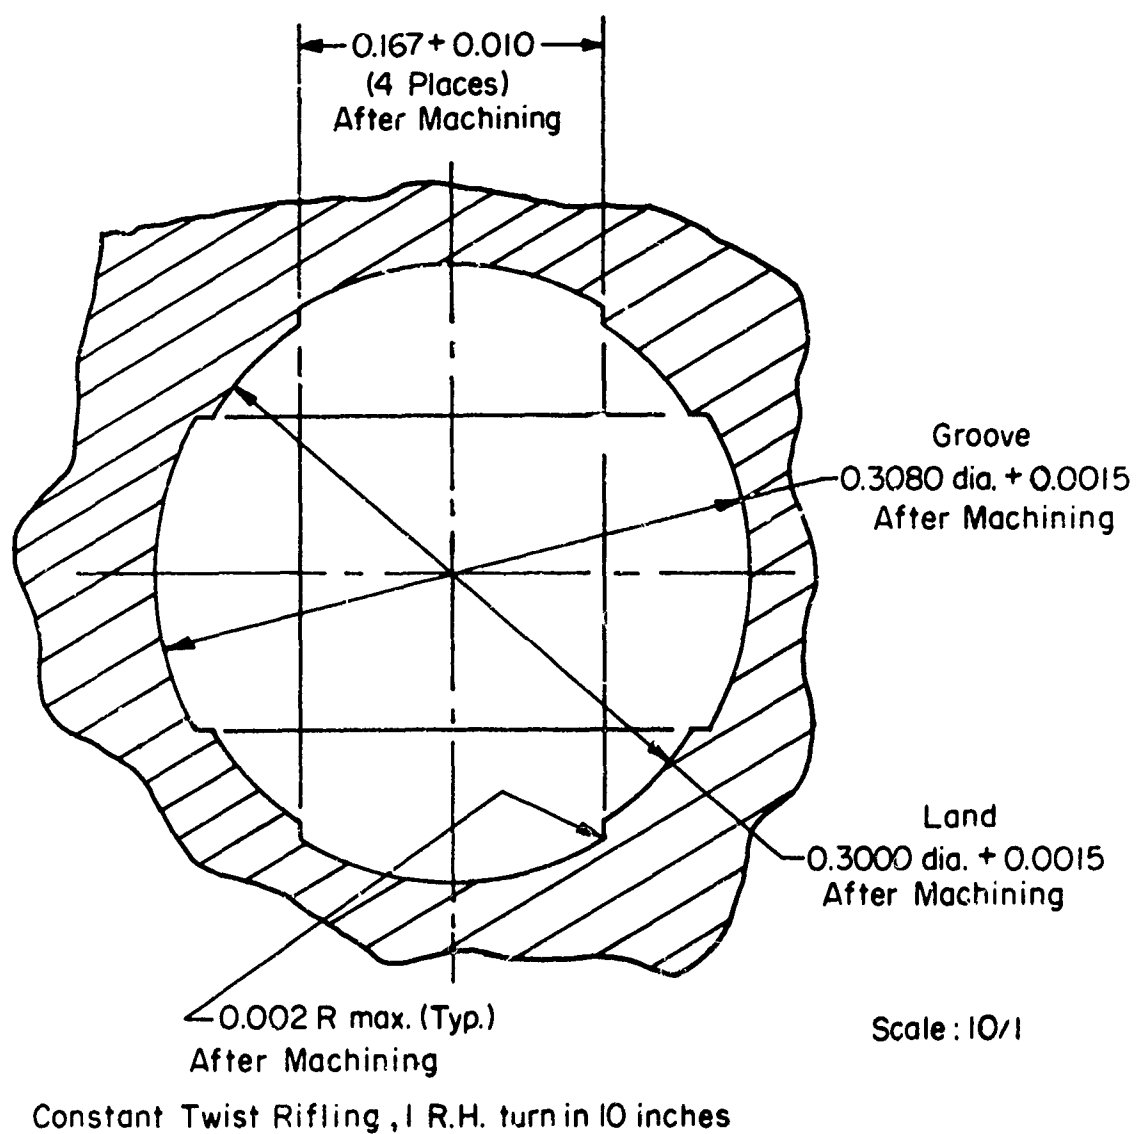


FIGURE 1

Interior Configuration,
7.62mm Gun Barrel

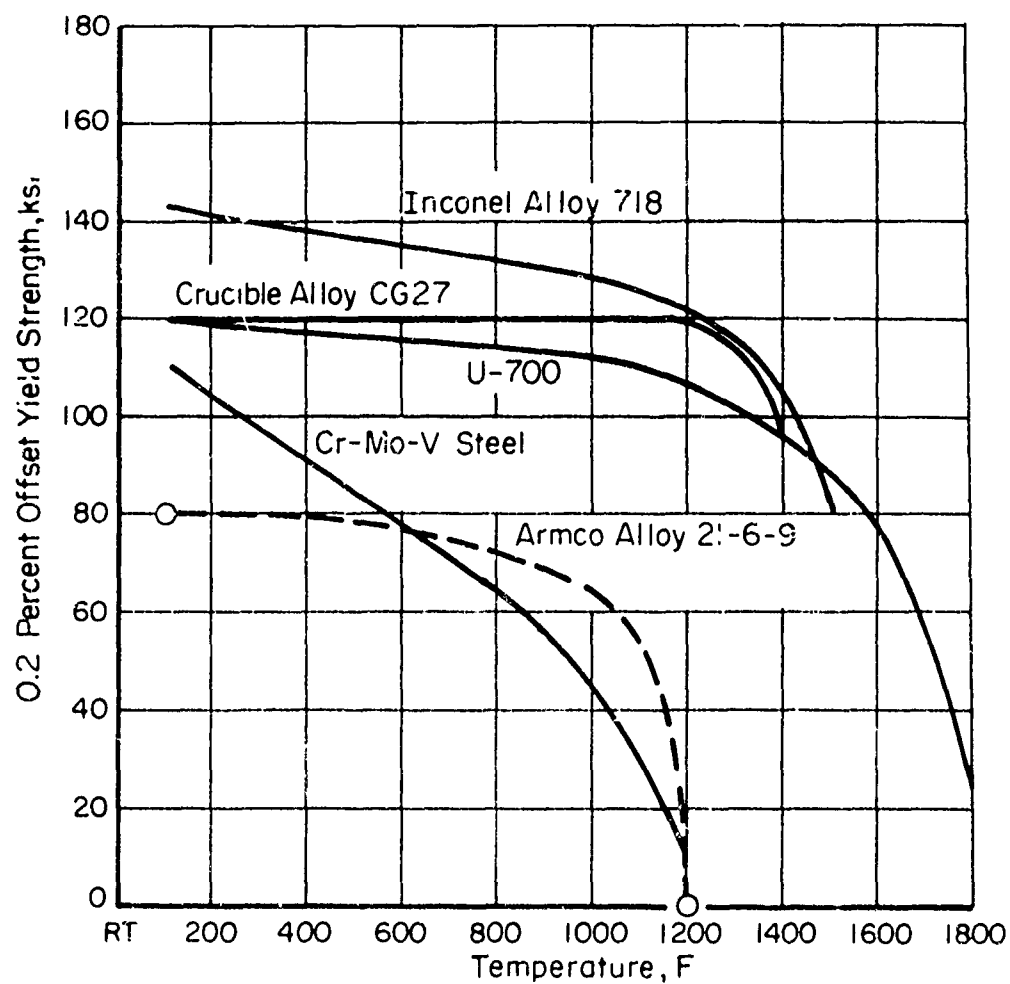

Note: Data for Armco Alloy 21-6-9 for room temperature and 1200 F only, curve is estimated.

FIGURE 2 High-Temperature Yield Strengths of Selected Gun Barrel Materials Compared to Cr-Mo-V Steel

The five companies listed below were consulted to learn more about the experience they have had in the swaging of gun barrels:

Cincinnati Milling Machine Company
Champion Tool and Die Company
Fellows Gear Shaper Company
Atrax Division of Wallace-Murray Corporation
Fenn Manufacturing Company

Champion Tool and Die Company, and Fellows Gear Shaper Company have had a great deal of experience in the production of gun barrels by swaging. Fellows uses a Multiflow machine, which they designed and manufacture. Champion uses an Intraform machine, which was designed and is manufactured by the Cincinnati Milling Machine Company.

The Atrax Division is a supplier of high-quality tungsten carbide rifling mandrels used in the swaging of gun barrels. Furthermore, they are the only known company, according to Champion and Fellows, that has the capability to machine the required precise rifling grooves in the carbide mandrels.

Fenn Manufacturing Company is a manufacturer of two- and four-die rotary swagers. They have not done any gun barrel swaging, but have had some experience with swaging of tubes with various internal configurations.

From the discussions with the appropriate personnel at the aforementioned companies, the conclusions were that (1) a two-die swager will not yield the required accuracy for cold swaging gun barrels, (2) a four-die swager with a very large capacity is required for gun barrel swaging, (3) full-length rifling mandrels cannot be used in the swaging of gun barrels because they will shear during the elongation of the workpiece, (4) short tungsten carbide mandrels must be used to swage the ID contour of gun barrels, and (5) neither the Cincinnati Intraform nor the Fellows Multiflow machine is capable of hot swaging.

EXPERIMENTAL WORK

Materials

The certified chemical compositions of the alloys selected for this investigation are given in Table I. The alloys were procured in the form of annealed, centerless ground rods. All materials except Crucible CG-27 were received in the condition ordered, which is given in Table II. After the Gun barrel blanks of CG-27 had been prepared, hardness measurements indicated that the alloy was supplied in the aged condition rather than in the solution-annealed condition. Therefore, the gun barrel blanks of CG-27 were annealed since this alloy would be expected to exhibit better cold-forming behavior in the annealed condition. The heat treatment of the CG-27 blanks is discussed later.

With the exception of Inconel 718, the rods of each alloy were 1.600 inches in diameter. Inconel 718 was ordered and received as 1.500-inch-diameter rods because this size was available from stock. In addition, 1.015-inch-diameter Inconel 718 rod was purchased for use in the preliminary cold swaging trials discussed in the following section.

Preliminary Cold-Swaging Trials

The Columbus Laboratories of Battelle has a 2-die rotary swager, made by Fenn Manufacturing Company, which was designed to handle rods up to a diameter of 3/4 inch. However, the Laboratories were informed by Fenn that the swager might well be capable of reducing the nominal 1.5 inch OD X 0.330-inch ID tubes required for the gun barrel blanks.

To determine the capabilities of the swager, a 1.015-inch-diameter round bar of Inconel 718 in the solution annealed condition (1950°F - 1 hour - air cooled) was cold swaged to approximately 20 per cent reduction in area in one pass. The rod was held manually. During the swaging operation, the swager nearly stalled. In addition, the Inconel 718 rod became slightly bent because of manual swaging.

On the basis of the results of the preliminary cold swaging trials, conclusions were that (1) the Fenn swager does not have enough capacity to form gun barrels from 1.5-inch-diameter tubes and (2) an elaborate special fixture would be required to hold the workpiece during the swaging operation to maintain straightness.

TABLE I CERTIFIED CHEMICAL COMPOSITION OF ALLOYS

Alloy	Chemical Composition, percent											
	Fe	Cr	Ni	Co	Mo	Cb	Ti	Al	Mn	C	Si	B
Inconel Alloy 718	19.14	17.70	52.99	0.21	3.04	5.40(a)	0.99	0.47	0.08	0.051	0.18	0.025
Armco Alloy 21-6-9	Balance	20.04	6.67	-	-	-	-	-	8.73	0.007	0.19	-
Udimet Alloy U 700	90.25	15.0	Balance	18.7	4.80	-	3.46	4.30	0.10(b)	0.07	0.10(b)	0.030
Crucible Alloy CG-27	Balance	12.74	37.46	-	5.68	0.91	2.55	1.61	-	0.07	-	0.009

(a) Cb + Ta

(b) Maximum

TABLE II SPECIFIED HEAT TREATMENT OF ALLOYS FOR
COLD-SWAGING TRIALS

Alloy	Specified Heat Treatment
Inconel Alloy 718	1950 F - 1 hour - air cool
Armco Alloy 21-69	1950 to 2050 F - 1 hour - rapid air cool
Udimet Alloy U 700	1925 F - 1 hour - air cool
Crucible Alloy CG-27	1875 to 1900 F - 1 hour - oil quench

Preparation of Gun Barrel Blanks

The rods of each alloy were cut and faced-off to a length of 20 inches. Then the rods were gun drilled and machined by Howard Dearborn, Inc., Berea, Ohio, into blanks designed as shown in Figure 3 to yield full-length gun barrels. The final OD of the Inconel 718 was slightly under 1.500 inches, since the starting diameter was only 1.500 inches. The major function of the machining operation was to obtain concentricity of the outer diameter (OD) and the inner diameter (ID) which is very critical in swaging gun barrel blanks.

Heat Treatment of Crucible Alloy CG-27 Blanks


As mentioned previously, heat treatment of the Crucible CG-27 gun barrel blanks was necessary since this material was not supplied in the solution-annealed condition.

Prior to heat treating all CG-27 blanks, a brief study was made to determine the effect of the heat-treating time and cooling method on the hardness and straightness of the alloy. Blank 41, a 3-3/4-inch-long piece of Blank 46, and 1-inch-long pieces of the undrilled 1.600-inch-diameter rod were annealed at 1900°F for 1 to 4 hours and air cooled or oil quenched.

The hardness data given in Table III indicated that, with air cooling, the optimum annealing time was between 2 and 3 hours. With oil quenching, the hardness dropped to a much lower hardness level.

In another experiment, a gun barrel blank, No. 41, was annealed in an argon atmosphere at 1900°F for 1 hour and air cooled. The straightness of this blank was off by a total indicator reading (T.I.R.) of only 0.002 inch.

Since the straightness of Blank 41 was very good, the remaining blanks of Crucible CG-27 were heat treated by use of air cooling rather than oil quenching, even though the terminal hardness was 15 Rockwell C points higher for air-cooled material. However, the higher hardness level was not expected to impair the swageability of the alloy, while the possibility of warpage occurring is reduced by air cooling rather than oil quenching.

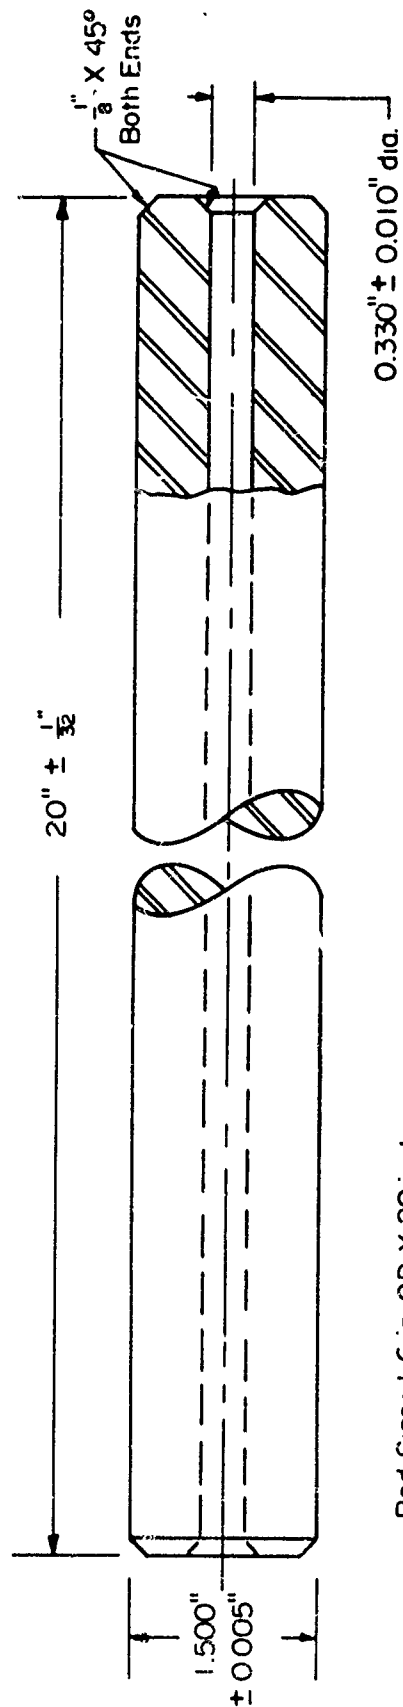

Rod Size: 1.6 in. OD X 20 in. Long
 OD-ID Concentric within 0.002 in. per in. as gun drilled
 ID Surface Finish: 125 RMS max.
 OD Surface Finish: 125 RMS max.

FIGURE 3

Gun Barrel Blank

TABLE III HARDNESS OF SAMPLES OF CRUCIBLE
ALLOY CG-27 HEAT TREATED AT 1900 F

Sample Number	Time at Temperature, hr	Cooling Method	Hardness, Rockwell C
461-462	1.0	Rapid air cool	34
4-1	2.0	Slow air cool	32
4-2	3.0	Slow air cool	33
4-3	4.0	Oil quench	17
461-462 ^(a)	1.0	Slow air cool	33

(a) This sample was given an additional 1 hour heat treatment and slow air cooled to determine the effect of cooling rate.

Thus, full-size Blanks 41, 42, 43, 44, and 45, and 2-1/2- and 9-inch lengths of Blank 46 were annealed in an argon atmosphere at 1900°F for 2-1/2 hours (Blank 41 had a total of 3-1/2 hours at 1900°F) and air cooled. The straightness of the full-length blanks varied from 0.003 to 0.007 inch T.I.R. The measurements for each blank were as follows:

<u>Blank</u>	<u>Straightness (In.) - T.I.R.</u>
41	0.007
42	0.004
43	0.006
44	0.003
45	0.0034

After the heat treatment, the Crucible CG-27 blanks were vapor blasted on the ID and OD to remove a slight oxide film and then cleaned thoroughly with water and acetone.

Evaluation of Gun Barrel Blanks

Machinability

The machinability rating of the alloys, based on facing off the ends, machining the OD, and gun drilling are as follows:

<u>Rating</u>	<u>Alloy</u>
1	Armco 21-6-9 (easiest to machine)
2	Udimet 700
3	Crucible CG-27
4	Inconel 718 (most difficult to machine)

Armco 21-6-9 was much easier to machine than any of the other alloys. On the other hand, a large difference did not occur in the machinability among Udimet 700, Crucible CG-27, and Inconel 718.

Surface Finish

Surface roughness measurements were made on the ID and OD of the gun barrel blanks of each alloy. A blank was sectioned for longitudinal measurement of the roughness along the surface of the ID and for metallographic studies. The surface finish was determined by centerline average (CLA) which has replaced the RMS method.

The following data show that a good surface was obtained on the ID by gun drilling. The OD surface was also quite smooth.

<u>Alloy</u>	<u>Sample</u>	<u>Surface Finish, Microinch</u>	
		<u>ID</u>	<u>OD</u>
Inconel 718	163B	52	70
Armco 21-6-9	263B	17	56
Udimet 700	363B	32	142
Crucible CG-27	463B	26	125

Metallographic Studies


A gun barrel blank of each alloy was cut into transverse and longitudinal sections and prepared for metallographic examination. Photomicrographs of the transverse sections at the ID of the alloys are presented in Figure 4.

Metallographic examination of Inconel 718 revealed the typical microstructure for this alloy in the solution-annealed condition (1950 F - 1 hour - air cool). The alloy consists of a generally fine-grained austenitic matrix containing a moderate amount of intragranular precipitates, presumed to be complex carbides and carbonitrides. In the longitudinal sample, the precipitates tended to be aligned in stringers running parallel to the long axis of the blank.


The microstructure of Armco 21-6-9 consists of a fine-grained austenitic matrix containing a small quantity of gray nonmetallic inclusions, presumed to be manganese sulfide. These inclusions tended to be aligned with the long axis of the blank in the longitudinal sample.

The microstructure of Udimet 700 consists of a very fine-grained, mottled austenitic matrix with a large quantity of inter- and intragranular precipitates, presumed to be complex carbides and carbonitrides. The precipitates are aligned in bands in the longitudinal direction. The pronounced banding indicates a lack of homogeneity in the alloy.

Examination of Crucible CG-27 revealed a very fine-grained, austenitic matrix containing generally small spherical inter- and intragranular precipitates, but with

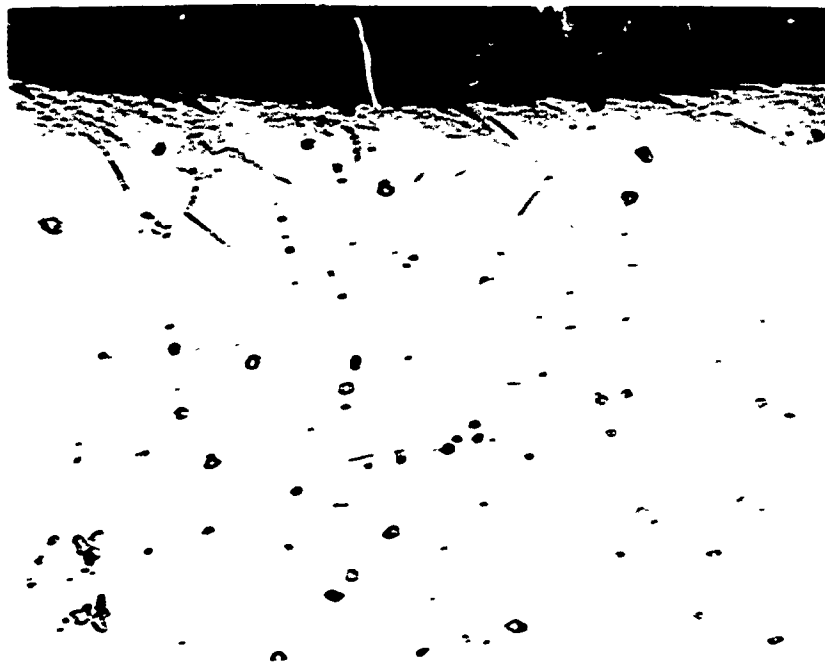


200X 20 Glycerine-20 HCl-10 HNO₃ 8E273
 Inconel 718: Sample No. 166
 Heat Treatment: 1950 F - 1 hour - air cool

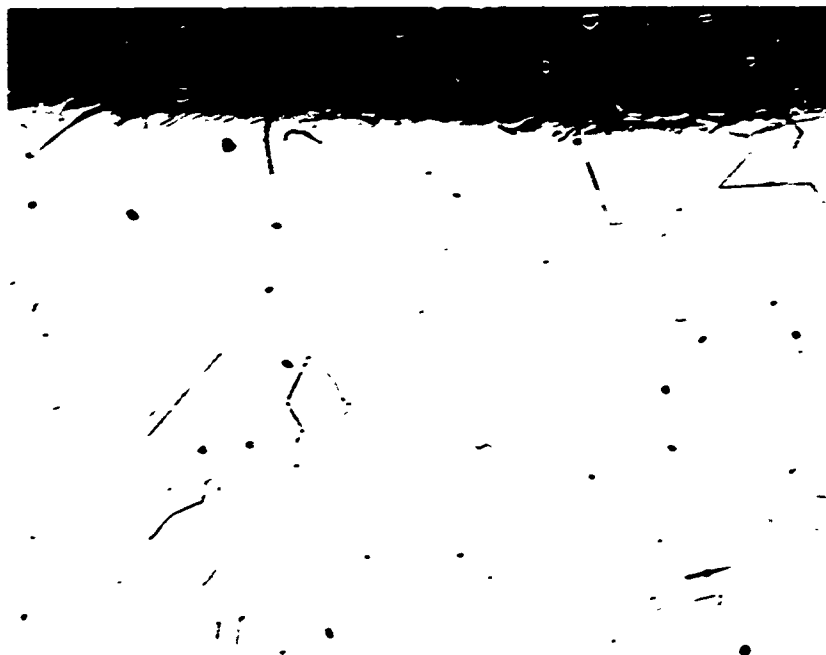

200X 20 Glycerine-20 HCl-10 HNO₃ 8E274
 Armco 21-6-9: Sample No. 266
 Heat Treatment: 1950-2050 F - 1 hour - rapid air cool

FIGURE 4 Transverse Sections of Gun Barrel Blanks

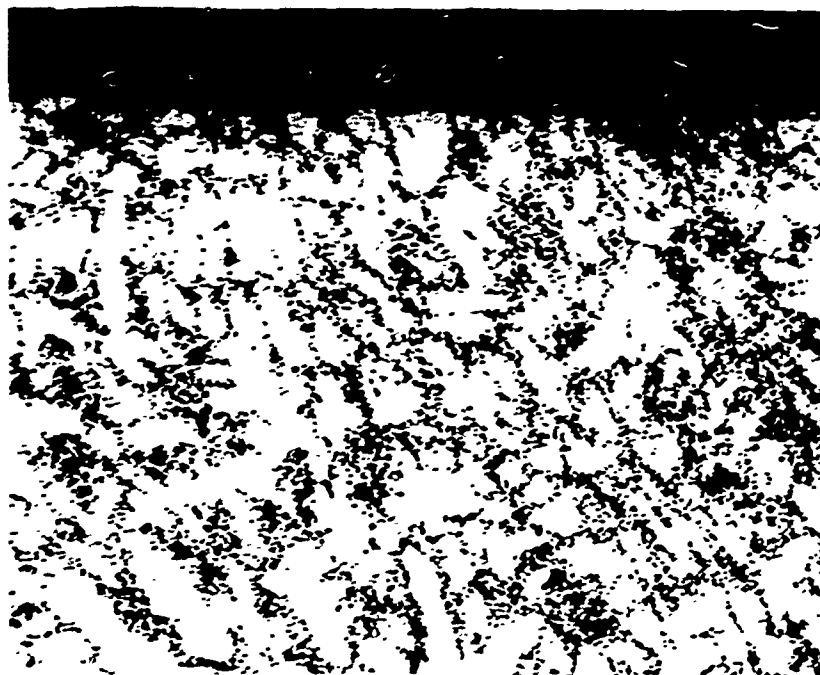

200X 95 HCl-2 HNO₃-1/2 g CuCl₂ 8E271
 Udimet 700: Sample No. 366
 Heat Treatment: 1925 F - 1 hour - air cool



200X 20 Glycerine-20 HCl-10 HNO₃ 8E275
 Crucible CG-27: Sample No. 468
 Heat Treatment: 1900 F - 2-1/2 hours - rapid air cool

FIGURE 4 (Continued)

Transverse Sections of Gun Barrel Blanks

a few large precipitates that appear to be titanium carbonitrides. A tendency exists for the small precipitates to be located intragranularly near the ID and OD, but intergranularly at the interior of the wall of the blank. The grain boundary precipitates are discontinuous. A slight longitudinal alignment of the precipitates occurs in the longitudinal sample.

Hardness Studies

Vickers hardness measurements were taken on the transverse metallographic samples of the gun barrel blanks of the alloys. Five hardness measurements were made along four radial traverses on each alloy. The radial traverses were approximately 45 degrees apart with impressions about 100 mils (0.1 inch) from each other.

The hardness data are presented in Table IV. These data indicate that the hardness of Inconel 718 is somewhat higher than expected, while the hardness of Armco 21-6-9 and Udimet 700 is just about the typical value for these alloys. The hardness of CG-27 is close to the anticipated value, based on the data obtained and presented in an earlier section of this report concerning the preparation of the gun barrel blanks. However, the hardness is about 19 Rockwell C points higher than that of material that is oil quenched rather than air cooled after solution annealing.

The data show that the hardnesses of Armco 21-6-9 and Udimet 700 are lowest near the ID and become increasingly higher toward the OD. On the other hand, Inconel 718 is hardest near the ID and becomes increasingly softer toward the OD. Crucible CG-27 shows a slight hardness trend similar to that of Inconel 718.

Based on the hardnesses of the alloys, Armco 21-6-9 and Inconel 718 were expected to exhibit the best formability during the swaging of the gun barrels. Crucible CG-27 was expected to exhibit slightly poorer forming behavior than Inconel 718, while the formability of Udimet 700 was expected to be less than that of Crucible CG-27.

Cold Swaging of Gun Barrels

Fellows Gear Shaper Company in Springfield, Vermont, was selected as the contractor for the swaging. Fellows was chosen because this company has (1) swaging machines

TABLE IV HARDNESS OF TRANSVERSE SECTIONS OF GUN BARREL BLANKS

Alloy(a)	Location of Hardness Impressions (b)	Hardness, VHN (10-kg Load)									
		Distance From ID, mils									
		85	185	265	385	485	Average (c)		Overall		
									Range	Average	(c)
Inconel Alloy 718 (166)	1	314	294	266	249	247	274	(27)	243-327	282	(28)
	2	294	281	274	272	243	272	(26.5)			
	3	304	309	283	289	283	292	(29.5)			
	4	327	285	285	283	276	290	(29)			
Armco Alloy 21-6-9 (266)	1	196	191	207	213	230	207	(14)	191-242	209	(14.5)
	2	193	205	209	212	240	211	(15)			
	3	198	201	205	209	225	207	(14)			
	4	197	193	209	215	242	211	(15)			
Udinex 700 (366)	1	397	397	413	401	413	404	(42)	394-437	405	(42)
	2	397	405	413	415	437	413	(43)			
	3	397	394	401	409	417	402	(42)			
	4	394	394	401	401	413	400	(41.5)			
Crucible Alloy CG-27 (468)	1	342	339	339	336	339	339	(35.5)	336-363	342	(36)
	2	342	342	348	348	336	343	(36)			
	3	339	339	342	351	342	342	(36)			
	4	336	342	342	351	363	347	(36.5)			

- (a) Heat treatment of each alloy is given in Table II. Numbers in parentheses are sample numbers.
- (b) The hardness impressions were taken along four radial traverses which were about 45 degrees apart.
- (c) Numbers in parentheses are Rockwell C hardness numbers converted from the Vickers hardness number. The converted Rockwell C hardness numbers are for reference only, since the accuracy of the conversion is not known.


capable of producing gun barrels with rifling grooves, (2) a great deal of experience with internal swaging of contours including the rifling in gun barrels, (3) offered to furnish the required tooling including swaging dies and mandrels, and (4) offered to conduct the swaging trials at a reasonable cost.

Equipment and Tooling

A photograph of the Fellows Multiflow machine used for the experimental cold swaging of the 7.62mm rifled gun barrels is shown in Figure 5. The Multiflow machine was designed and built by Fellows. It is a stationary 4-die machine with a 500-ton load capacity. The machine has automatic feeding and positioning mechanisms which position the mandrel in the dies, rotate the blank counterclockwise and feed the blank over the mandrel and through the swaging dies. The mandrel is held in a predetermined axial position in the dies, but is free to rotate. During the swaging operation, the dies and blank are flooded with a coolant called Mentor 28.* The dies contact the blank at the rate of 1500 times per minute. A work receiver located on the exit side of the die exerts back pressure on the gun barrel blank, as it leaves the die, which helps maintain the straightness of the blank during swaging. The work receiver is hollow so that the coolant, Mentor 28, can be forced into the bore of the gun barrel blank during swaging to cool the mandrel and the blank. After the blank is formed, the dies automatically open, the receiver pushes the blank back to its original starting point, and the finished blank is lifted from the machine cradle.

A drawing (Fellows Drawing D-4324-FA) of the dies designed by Fellows Co. and used in the swaging of gun barrel blanks is included as Figure 6. The dies were made from SAE M2 nonresulphurized steel hardened to 59 to 61 Rockwell C and bright stress-relieved after the profile section of the dies was finished.


*A product of Esso International, Inc., New York, New York 10019

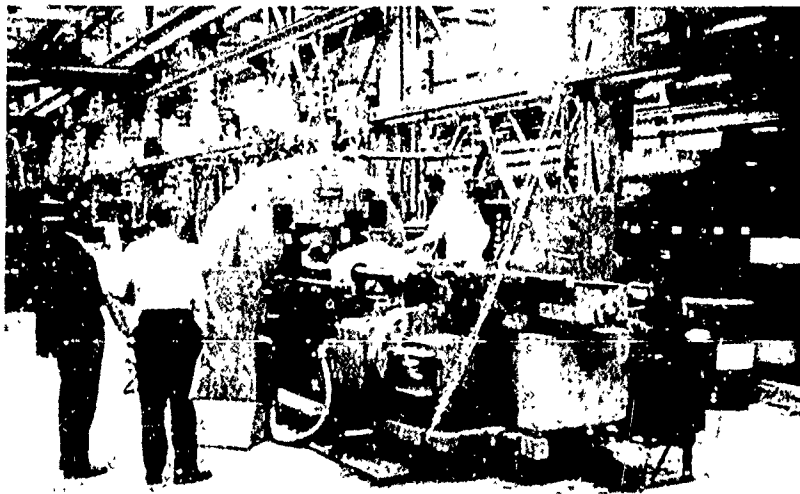

Reproduced from
best available copy. 

FIGURE 5

Multiflow Machine During Cold
Swaging of Gun Barrel Blanks

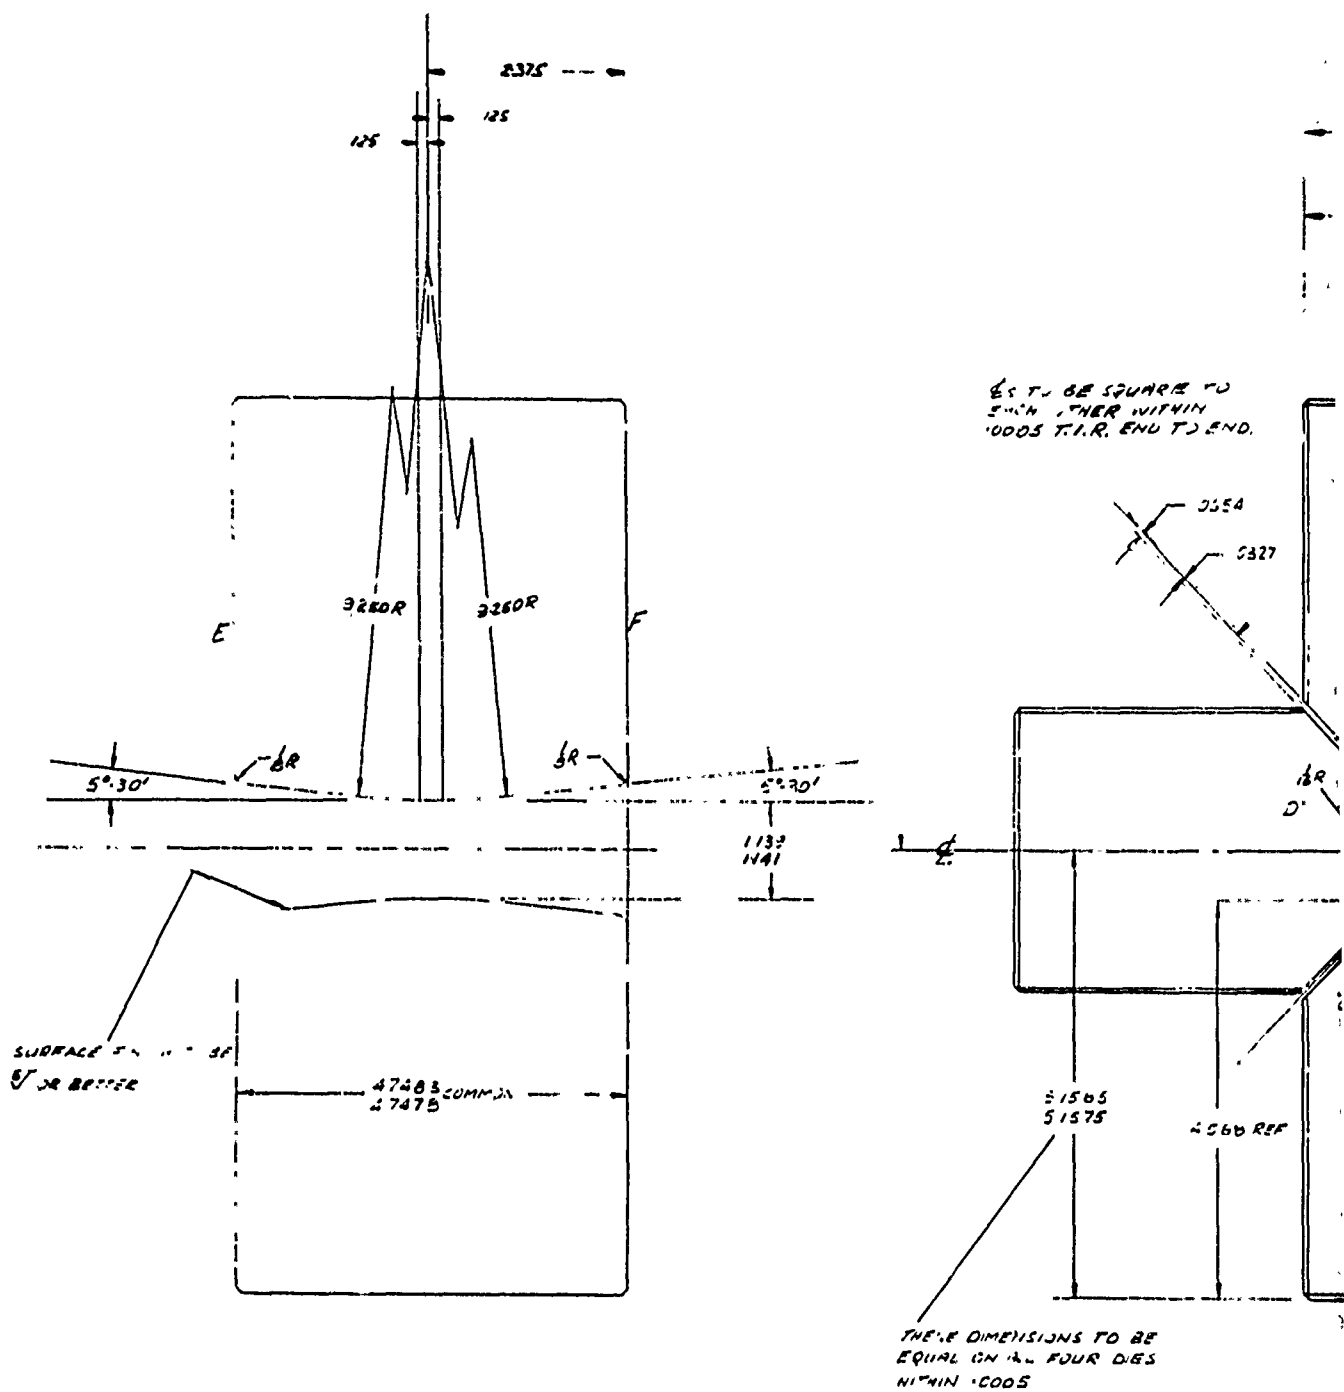


MATL. SAE M2 NON RESULPHURIZED (FSS. N910 PL)
HARDEN TO RC 53-61
AFTER FINISHING OF PROFILE SET IN BRIGHT STRESS RELIEF

OPERATING

19.1

19.

FIGURE 6. DRAWING OF D
IN MULTIFLOW

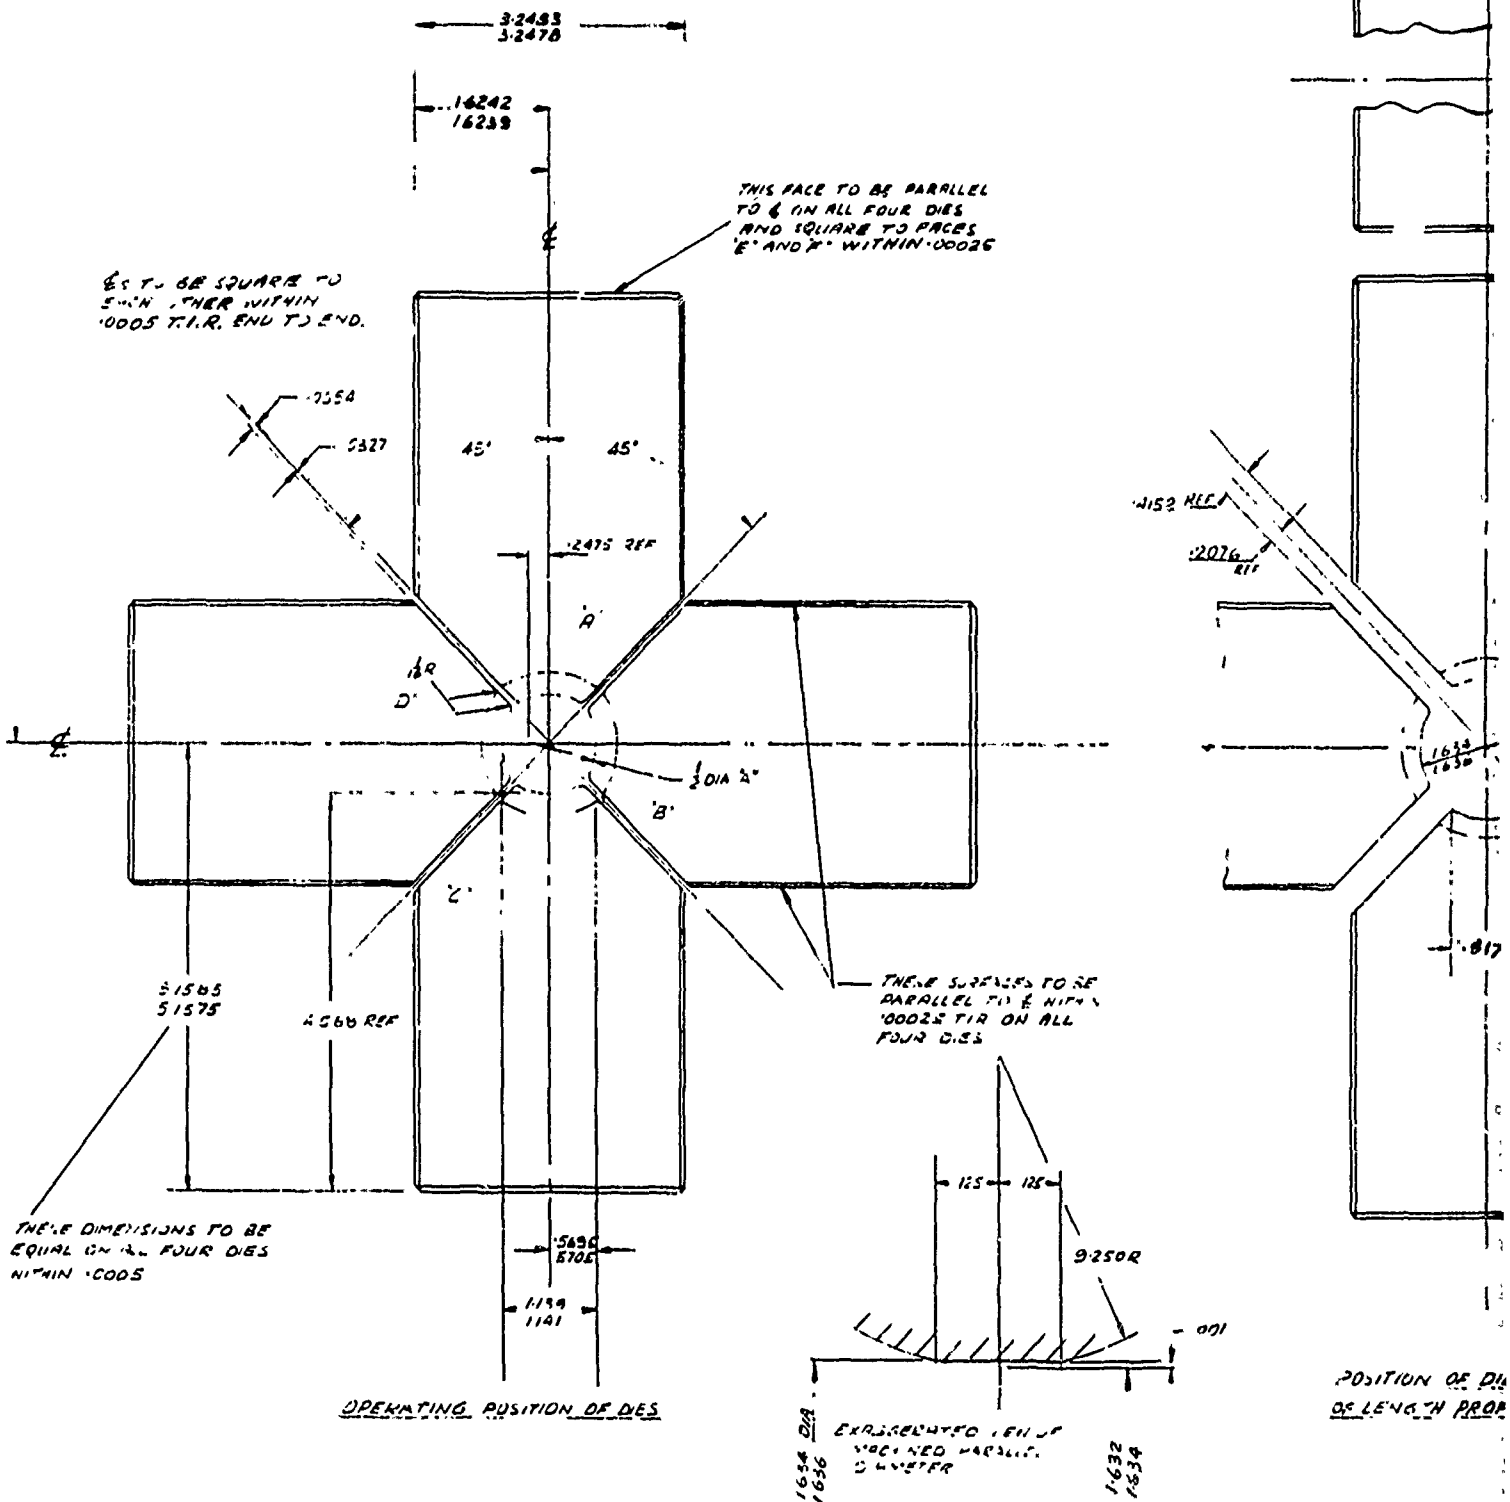


19.2


FIGURE 6. DRAWING OF DIES USED TO COLD SWAGE GUN BARRELS IN MULTIFLOW MACHINE

19.3

THIS FACE TO BE PARALLEL
TO G ON ALL FOUR DIES
AND SQUARE TO FACES
E AND F WITHIN .00025

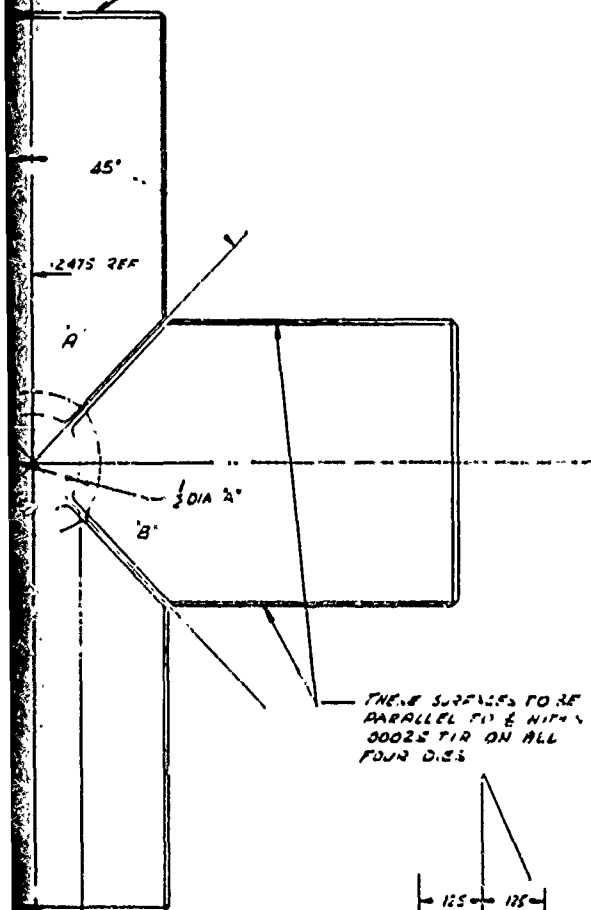


THESE SURFACES TO BE
PARALLEL TO G WITHIN
.00025 TIR ON ALL
FOUR DIES

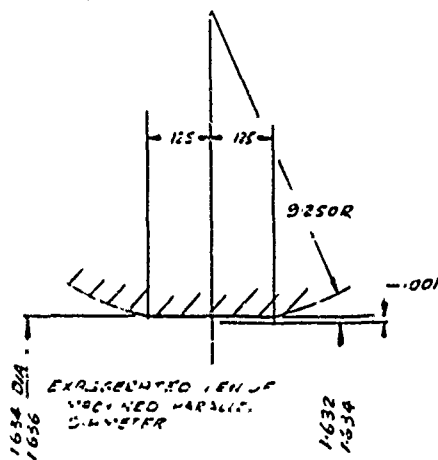

SECTION OF DIES

EXAGGERATED VIEW OF
MOUNTED PARALLEL
COUNTER

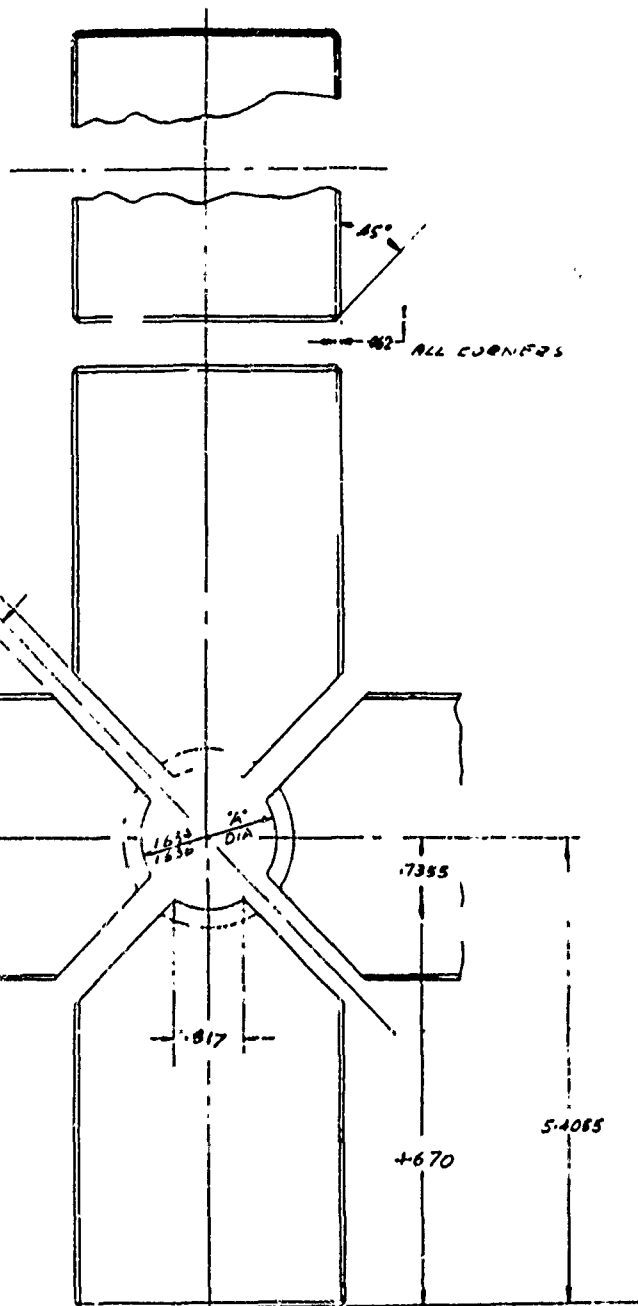

5.4085

+670

THIS DIM TO BE EQUAL
ON ALL FOUR DIES WITHIN
.0005 TIR

POSITION OF DIES FOR MACHINING
OF LENGTH PROFILE

USED TO COLD SWAGE GUN BARRELS
MACHINE

A drawing (Fellows Drawing 65-05-1047-2) of the rifling mandrel is shown in Figure 7. The mandrel was designed by Fellows Co. to produce the specified bore for the 7.62mm gun barrels. Three mandrels were made for Fellows by Atrax Division of Wallace-Murray Corporation who, according to several sources including Fellows, is the only company that has the capability of machining the rifling in the mandrels. One mandrel was machined from General Electric Carboloy, Grade 248, while the other two were machined from General Electric Carboloy, Grade 55B. Both grades performed well.

The rifling mandrel was silver soldered to the mandrel holder, which was described earlier.

Procedure

The following procedure was followed in swaging the gun barrel blanks:

- (1) The ID and OD of each gun barrel blank was cleaned thoroughly with acetone and then swabbed with a gun cleaning rod and dry cloth swabs.
- (2) The ID of each blank was coated thoroughly by swabbing and then pouring Houghton Cindol 624* lubricant through the blank.
- (3) The blank was placed on the cradle of the Multiflow machine.
- (4) The automatic sequencing was started in which the blank was positioned, the mandrel was inserted through the blank and positioned in the die, the driver and the receiver engaged the blank, and the blank was rotated and fed into the pulsating swaging dies.

*A product of E. F. Houghton Company, Philadelphia, Pa. 19133

- (5) After the gun barrel blank was formed, the dies automatically opened, the receiver blank pushed the blank back to its original position, the mandrel was extracted and the blank returned to the cradle of the machine.
- (6) The gun barrel blank was removed from the machine and the trailing end (about 10 inches) of the blank was immersed in a bucket of water. The water served to cool the blank and to clean out the lubricant.
- (7) The ID of the barrel blank was cleaned with water-soaked swabs on a gun cleaning rod.
- (8) The ID of the barrel blank was dried with swabs on gun-cleaning rods.
- (9) The ID of the barrel blank was inspected by a borescope.

Results and Discussion

Five gun barrel blanks each of Inconel 718, Armco 21-6-9, and Crucible CG-27 and seven gun barrels of Udimet 700 were formed by cold swaging blanks of each alloy. Data taken during the cold swaging trials are given in Appendix A. A typical gun barrel blank of each alloy is shown in Figure 8. The length of the swaged blanks ranged from about 25-1/8 to 27-9/16 inches; the OD ranged from 1.260 to 1.330 inches, dependent upon the die closing setting (wedge position dial numbers in Table A-1).

No severe problems were encountered during the swaging of the blanks except with Crucible CG-27. Pickup of material on the mandrel occurred during the first three swaging trials with this alloy. Changing the following variables of the swaging process eliminated pickup on the mandrel:

- (1) Feeding rate of the blank was decreased from 20 to 12 inches per minute.
- (2) Rotational speed of the blank was decreased from 130 to 105 rpm.
- (3) Thickness of the shims behind each of one pair of dies was increased from 0.004 to 0.008 inch.



- No. 1: Barrel No. 15 - Inconel Alloy 718
- No. 2: Barrel No. 25 - Armco Alloy 21-6-9
- No. 3: Barrel No. 35 - Udimat 700
- No. 4: Barrel No. 45 - Crucible Alloy CG-27

FIGURE 8 Gun Barrel Blanks Formed by Cold Swaging

Evaluation of Swaged Blanks

Nondestructive Testing

The bore of each gun barrel blank was examined twice with a borescope. A cursory borescopic examination was made at Fellows Co. immediately after each gun barrel blank was formed. A detailed examination of the bore of each blank was made later. With the exception of the first three swaged gun barrel blanks (Nos. 41, 42, and 43) of Crucible CG-27, the examinations indicated that the rifling detail was good and the surface was smooth and free of cracks. However, several of the blanks (Nos. 11, 14, 21, and 33) contained small defects that appeared to be an inherent defect in the material, rather than one caused by swaging. Pickup of material on the mandrel caused longitudinal scuffing along the lands of the Crucible CG-27 blanks (Nos. 41, 42, and 43). Thus, these three CG-27 blanks (Nos. 44 and 45) have good bore surfaces.

Surface roughness measurements were taken on the ID of one as-swaged gun barrel blank of each alloy. A longitudinal section of the blank was used, and the finish along a longitudinal traverse was determined by the CLA method used earlier to determine the finish of the gun barrel blanks.

The surface finish data for the ID of the cold-swaged gun barrel blanks, and for the ID of the gun drilled blanks, are presented in Table V. These data show that the surface finish of the ID of the swaged blanks is much better than that of the gun drilled blanks. Furthermore, the surface finish of the ID is better than that (25 microinches) specified for 7.62mm gun barrels in Rock Island Arsenal Drawing 11701204, dated April 14, 1965.

Inspection of the OD of the swaged blanks by use of dye penetrant indicated that all were free of cracks. Diameter measurements showed that maximum out-of-roundness was 0.001 inch.

Straightness measurements revealed that, in general, the straightness of the blanks was off from 0.003 to 0.009 inch T.I.R. However, two Inconel 718 blanks had 0.013 inch T.I.R., while another Inconel 718 blank had 0.026 inch T.I.R. Generally, the barrel blank with the largest deviation was sectioned for metallographic examination and hardness determination, although the quality of the bore was also a determining factor.

TABLE V SURFACE FINISH OF BORE OF GUN DRILLED BLANKS AND SWAGED BLANKS

<u>Alloy</u>	<u>Blank Sample Number</u>		<u>Surface Finish, CLA, Microinch</u>	
	<u>Swaged</u>	<u>Gun Drilled</u>	<u>Swaged</u>	<u>Gun Drilled</u>
Inconel 718	125A	163B	10	52
Armco 21-6-9	225B	263B	12	17
Udimet 700	375A	363B	7	32
Crucible CG-27	451	463B	12	26

A tabulation of the diameter and straightness measurements is presented in Appendix B.

On the basis of the borescopic examination of the bore and the straightness measurements, a quality rating was assigned to each barrel blank. The ratings, given in Table VI, were made by a comparison of the blanks of the same alloy, rather than by a comparison of all blanks with each other.

Metallographic Examination of As-Swaged Samples of Gun Barrel Blanks

Longitudinal and transverse sections of one or more blanks of each alloy were removed and prepared for metallographic examination and hardness determinations.

Photomicrographs of transverse and longitudinal sections of a gun barrel blank sample of each alloy at the bore surface are shown in Figures 9 through 12. These photomicrographs show that the surfaces of the as-swaged samples of each alloy are very smooth. Also, the sharp detail of the lands for each of the samples can be seen.

The gun barrel blank sample of Udimet 700 contained occasional microtears along the bore surface at areas where precipitates intersected the bore surface. These microtears run about 1-mil deep and can be seen in Figure 11.

The microstructures of the as-swaged samples of all four alloys were similar to those observed in the samples of the gun drilled blanks, although slight differences occurred that had been produced by cold swaging. For example, the Inconel 718 and the Udimet 700 samples tended to have a shallow (from 0.5 to 1.5 mils deep) cold-worked layer along the bore. The Inconel 718 sample (Figure 9) contained coring lines throughout the longitudinal section. These coring lines indicate the existence of slight inhomogeneity in the chemical composition of the alloy. Armco 21-6-9 (Figure 10) also contained the coring lines as well as pronounced mechanical twins within the grains.

The grains in the transverse samples of each alloy are equiaxed and do not appear to be deformed. On the other hand, the grains in the longitudinal samples of Inconel 718, Armco 21-6-9, and Crucible CG-27 are elongated in a direction parallel to the axis of the blank. The longitudinal sample (Figure 11) of Udimet 700, however, does not show any appreciable evidence of cold work caused by swaging.

TABLE VI QUALITY RATING OF EXPERIMENTAL 7.62-mm GUN BARRELS

Gun Barrel Blank	Alloy	Quality ^(a) Rating
11	Inconel 718	4
12	Inconel 718	5
13	Inconel 718	2
14	Inconel 718	3
15	Inconel 718	1
21	Armco 21-6-9	1
22	Armco 21-6-9	5
23	Armco 21-6-9	3
24	Armco 21-6-9	4
25	Armco 21-6-9	2
31	Udimet 700	3
32	Udimet 700	5
33	Udimet 700	6
34	Udimet 700	2
35	Udimet 700	4
37	Udimet 700	7
38	Udimet 700	1
41	Crucible CG-27	5
42	Crucible CG-27	3
43	Crucible CG-27	4
44	Crucible CG-27	1
45	Crucible CG-27	2


(a) A rating of "1" indicates, for a particular alloy, the barrel with the highest quality.



200X

20 Glycerine-20 HCl-10 HNO₃
Transverse Sample No. 126

8E269

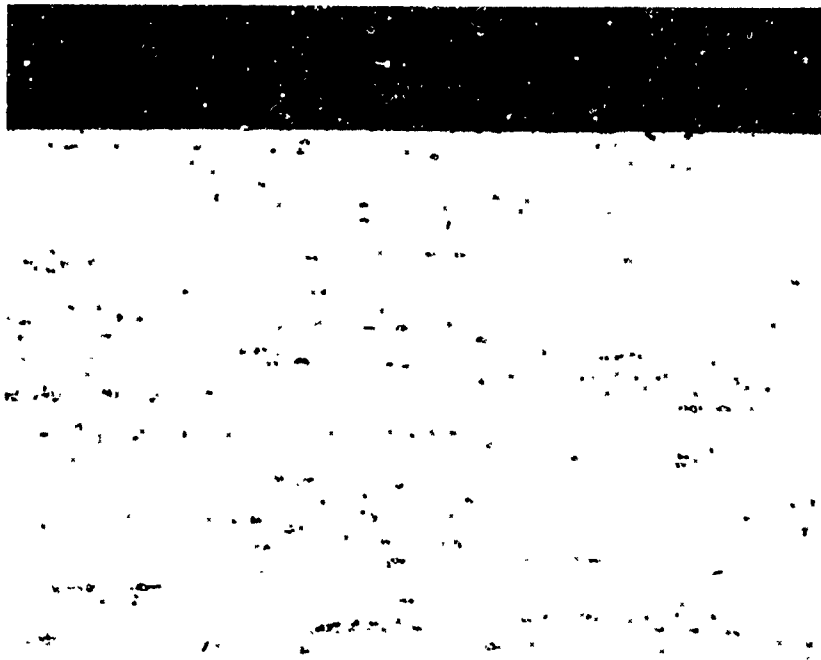


55X

20 Glycerine-20 HCl-10 HNO₃
Longitudinal Sample 125BB

8E277

FIGURE 9 As-Swaged Inconel 718 Gun Barrel Samples

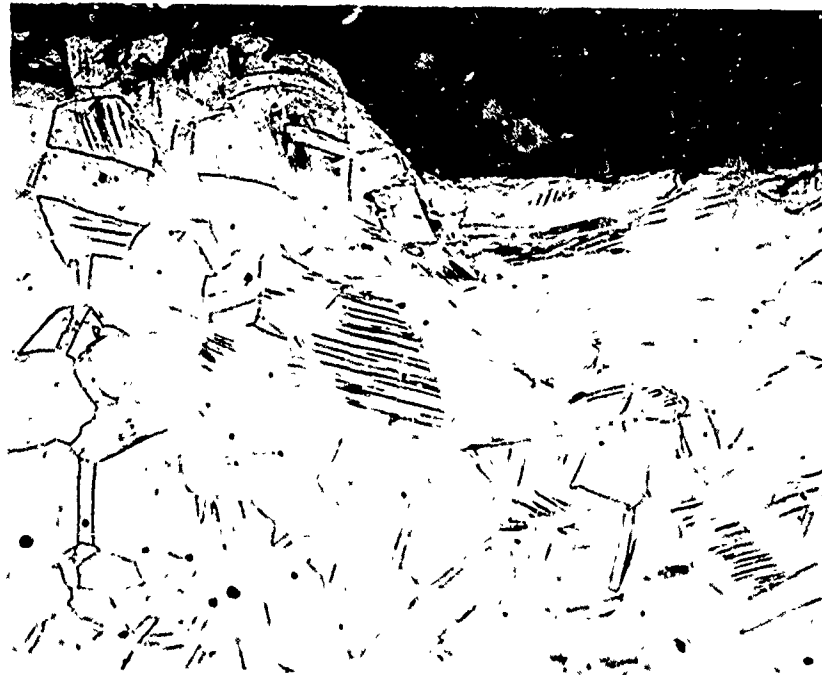

200X

40 HCl-10 HNO₃
Transverse Sample No. 226

8E268




55X

20 Glycerine-20 HCl-10 HNO₃
Longitudinal Sample No. 225BB

8E280


FIGURE 10 As-Swaged Armco 21-6-9 Gun Barrel Samples

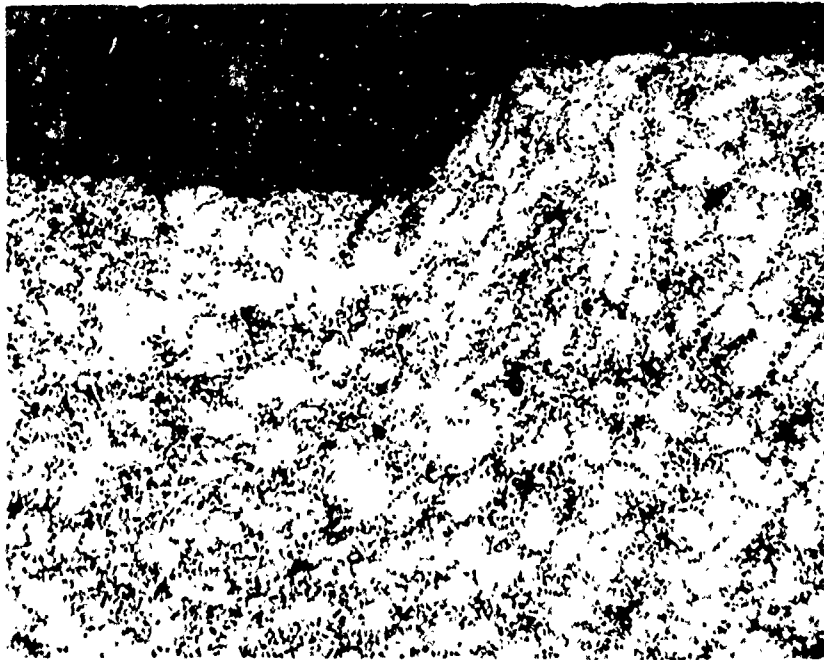

200X

95 HCl-2 HNO₃-1/2 g CuCl₂
Transverse Sample No. 376

8E270

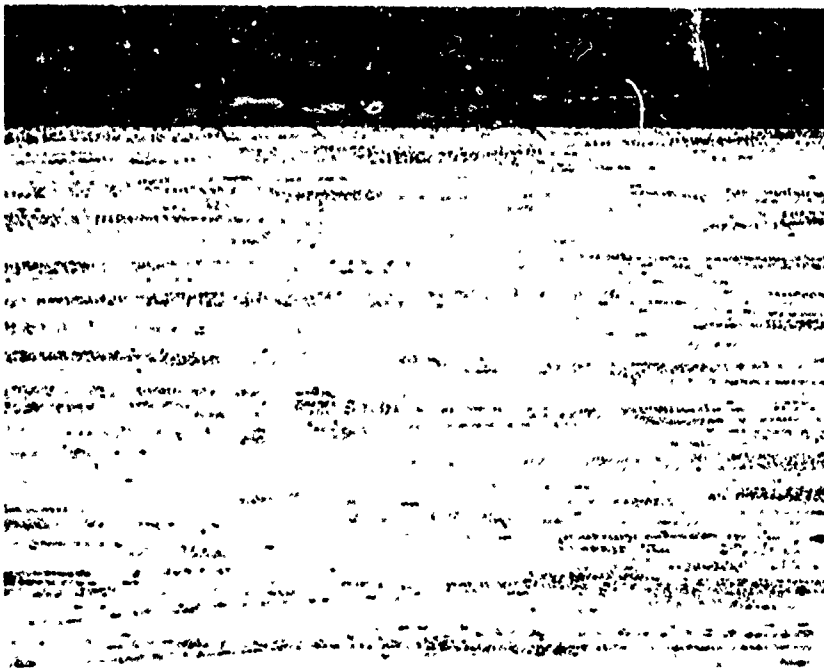


55X

As Polished
Longitudinal Sample No. 375BB

8E278

FIGURE 11 As-Swaged Udmet 700 Gun Barrel Samples

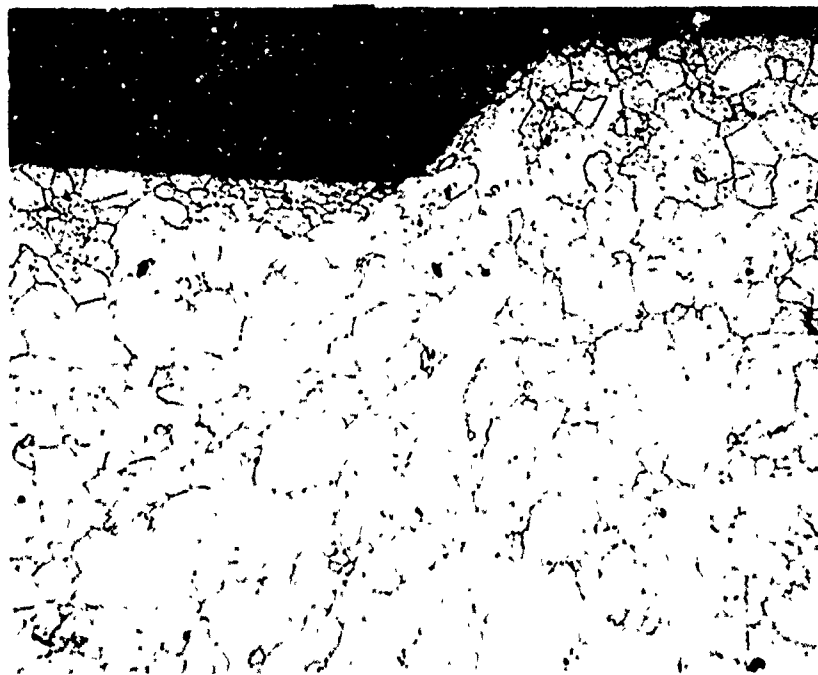

200X

40 HCl-10 HNO₃
Transverse Sample No. 452

8E267



55X

20 Glycerine-20 HCl-10 HNO₃
Longitudinal Sample No. 451 B

8E276

FIGURE 12 As-Swaged Crucible Alloy CG-27 Gun Barrel Samples

Metallographic Examination of Heat-Treated Samples of Gun Barrel Blanks

Three of the four selected gun barrel materials, Inconel 718, Udimet 700, and Crucible CG-27, are age-hardenable. Thus, they are normally annealed and aged to develop maximum strength before being placed in service. The usual heat treatments for the three alloys are given in Table VII. Armco 21-6-9 is not hardenable by heat treatment; however, it is hardenable by working such as cold swaging.

TABLE VII HEAT TREATMENTS FOR AGE-HARDENABLE, SELECTED
 GUN BARREL MATERIALS

Udimet 700

Solution annealing:	2150°F/4 hr/AC
High-temperature aging:	1975°F/4 hr/AC
Intermediate aging:	1550°F/25 hr/AC
Final aging:	1440°F/16 hr/AC

Inconel 718

Anneal:	1800°F/1 hr/AC
Age:	Hold 8 hr at 1325°F, furnace cool to 1150°F at the rate of 100°F/hr, hold at 1150°F for 8 hr and air cool.

Crucible CG-27

Solution annealing:	1875 to 1900°F for 1/2 hr/OQ
Intermediate aging:	1450°F/16 hr/AC
Final aging:	1200°F/16 hr/AC

Transverse samples of the gun barrel blanks in the as-swaged condition were heat treated according to the treatments given in Table VII. These samples were used for metallographic and hardness studies. The only deviation was that the annealing time used for Inconel 718 was 1-1/2 hours rather than 1 hour.

Because of the concern regarding the effect of high-temperature annealing on straightness and on bore dimensions of gun barrels, additional transverse samples of age-hardenable alloys were given the aging heat treatment without annealing.

For all heat treatments, the following procedure was used:

- (1) Each sample was degreased thoroughly with C.P. acetone.
- (2) Each sample was sealed in a clean vycor tube after evacuating to about 10^{-5} torr, flushing several times with high-purity argon and then backfilling to about 1/2 atmosphere with the argon.
- (3) The sample was annealed and aged or aged only according to the schedule in Table VII, except as previously noted for the Inconel 718 specimen. In the solution annealing of Crucible CG-27, the vycor tube was broken intentionally during the oil quench. The aging treatment for this sample was conducted in air.

The heat treatments of the various gun barrel blank samples are given in Table VIII.

Microstructures of transverse sections of the heat-treated samples of the swaged blanks are illustrated in Figures 13 through 15. The metallic layer along the core surface is a plating of nickel which was used to prevent rounding of the edges of the samples during preparation for metallographic examination.

Heat treatment of Inconel 718 resulted in a slight coarsening of the grains and the formation of a discontinuous grain-boundary phase or phases (believed to be a carbide or carbides) along with some intragranular precipitation (compare Figures 9 and 13). Examination of the sample revealed no cracking.

Heat treatment of Udimet 700 produced considerably larger grains than were present in the as-swaged sample. The heat-treated sample contains much fewer intergranular and intragranular precipitates (presumably carbides) than did the as-swaged sample, as can be seen by comparison of Figures 11 and 14. Several microtears where precipitates intersected the surface were observed, as noted earlier for the as-swaged samples.

TABLE VIII HEAT TREATMENTS USED FOR TRANSVERSE SAMPLES
OF GUN BARREL BLANKS

Sample	Alloy	Heat Treatment ^(a)
126	Inconel 718	Solution annealed and aged
126B ^(b)	Inconel 718	Aged
376	Udimet 700	Solution annealed and aged
376B ^(b)	Udimet 700	Aged
452	Crucible CG-27	Solution annealed and aged
422 ^(b)	Crucible CG-27	Aged

(a) Refer to Table VII for details of the heat treatments, except that the Inconel 718 specimen was solution-annealed for 1-1/2 hours rather than 1 hour.

(b) These samples were sent to the U. S. Army Weapons Command at Rock Island for evaluation.



200X

20 Glycerine-20 HCl-10 HNO₃
Transverse Sample No. 126

8E885

Heat Treatment: 1800 F-1-1/2 hour-air cool
1325 F- 8 hours-furnace cool to 1150 F
1150 F- 8 hours-air cool

FIGURE 13

Heat-Treated Inconel 718
Gun Barrel Sample



200X

20 Glycerine-20 HCl-10 HNO₃
Transverse Sample No. 376

8E886

Heat Treatment: 2150 F-4 hours-air cool
1975 F-4 hours-air cool
1550 F-25 hours-air cool
1440 F-16 hours-air cool

FIGURE 14

Heat-Treated Udimet 700
Gun Barrel Sample



200X

20 Glycerine-20 HCl-10 HNO₃
Transverse Sample No. 452

8E884

Heat Treatment: 1875 F-1-1/2 hours-oil quench
1450 F-16 hours-air cool
1200 F-16 hours-air cool

FIGURE 15

Heat-Treated Crucible CG-27
Gun Barrel Sample

Heat treatment of Crucible CG-27 caused a slight refinement of the grain structure. Most small intra-granular precipitates present in the as-swaged sample (Figure 12) were apparently dissolved by the heat treatment (Figure 15). Heat treatment had no appreciable effect on grain-boundary precipitate which remained discontinuous. No evidence of cracking was observed in the heat-treated sample of Crucible CG-27.

Photomicrographs of the heat-treated samples of Inconel 718, Udimet 700, and Crucible CG-27 are shown in Figures 16, 17, and 18, respectively. A photomicrograph of the as-swaged sample of Armco 21-6-9 which was not heat treated is included as Figure 19. These photomicrographs show the contour of the bore discussed in the next section.


Bore Dimensions

The bore of the same metallographic sample (a transverse section) of each alloy was measured in the as-swaged condition and after heat treatment. A Tukon hardness tester with a stage and filar eyepiece was used for determining the bore dimensions to the nearest 0.0001 cm. These measurements were converted to inches.

The data in Table IX show that the bore dimensions of the gun barrel blank samples before and after heat treatment are within (or no more than 0.0003 inch over) those allowable by Rock Island Arsenal Drawing 11701204, which specifies 0.300 ± 0.0015 inch and 0.308 ± 0.0015 inch for the diameters between the lands and grooves, respectively. The heat treatment caused the bore dimensions of the alloys to decrease from 0.0007 to 0.0016 inch.

The roundness of all the as-swaged blanks was very good, as may be seen from the data in Table IX. Heat treatment improved the roundness of Udimet 700, while it decreased very slightly the roundness of Inconel 718 and Crucible CG-27.

Apparently, gun barrel blanks of the age-hardenable alloys can be heat treated without destroying the bore dimensions.

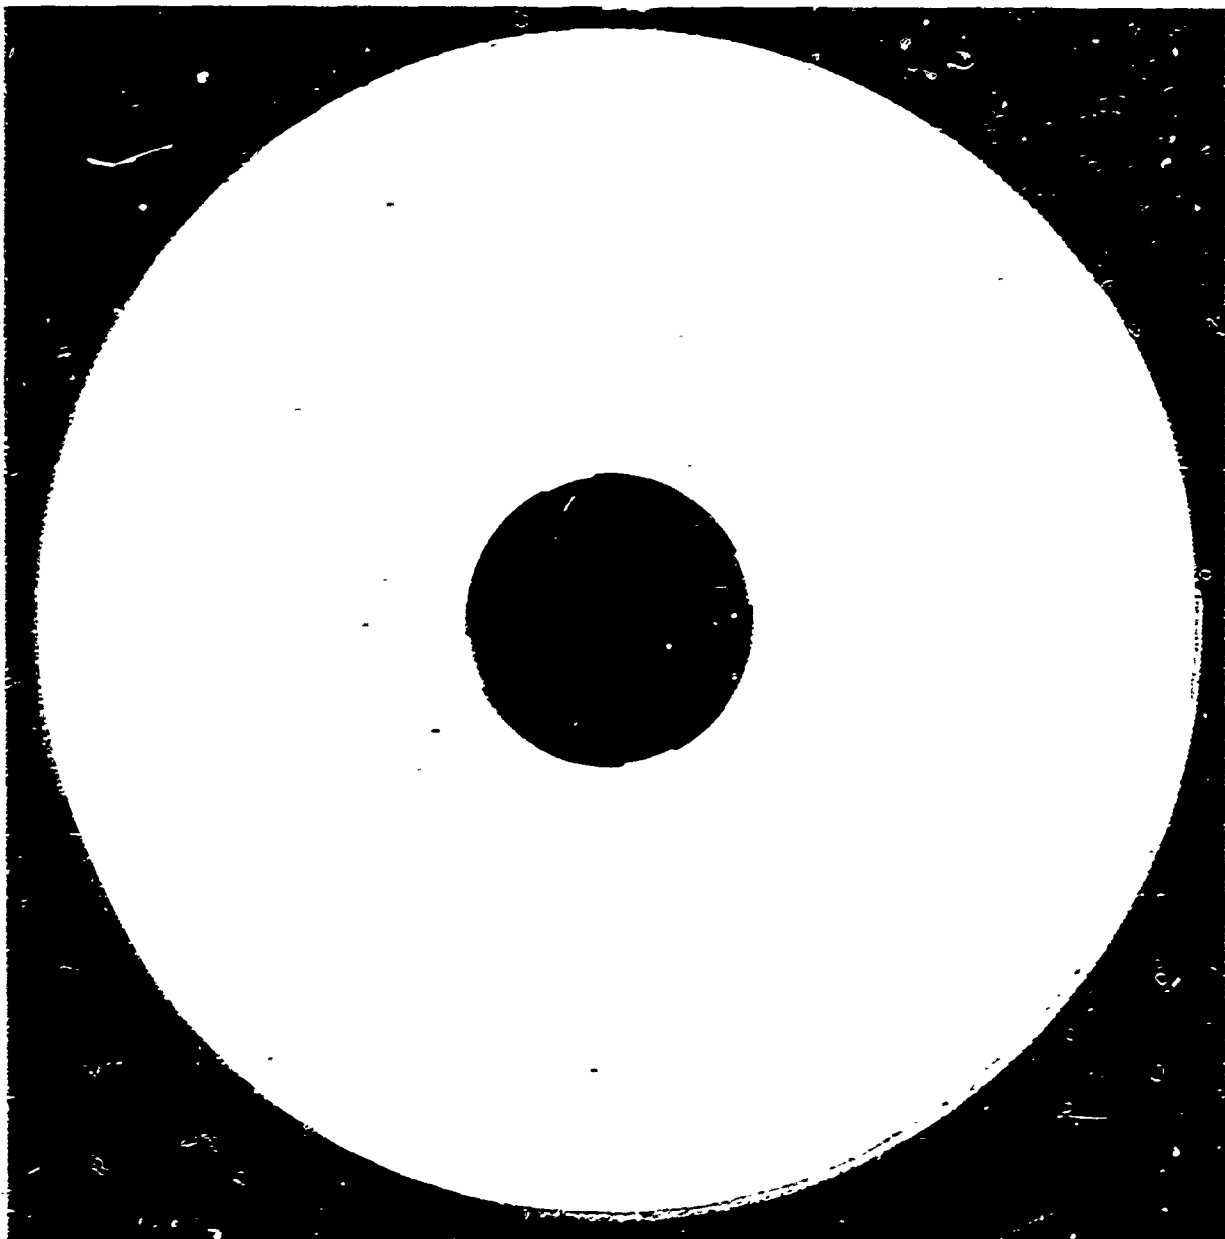


5X

20 Glycerine-20 HCL-10 HNO₃

8E925

Heat Treatment: 1800 F-1-1/2 hour<-air cool
1325 F-8 hours-furnace cool to 1150 F
1150 F-8 hours-air cool

FIGURE 16 Transverse Section of Heat-Treated
Inconel 718 Gun Barrel Sample 126

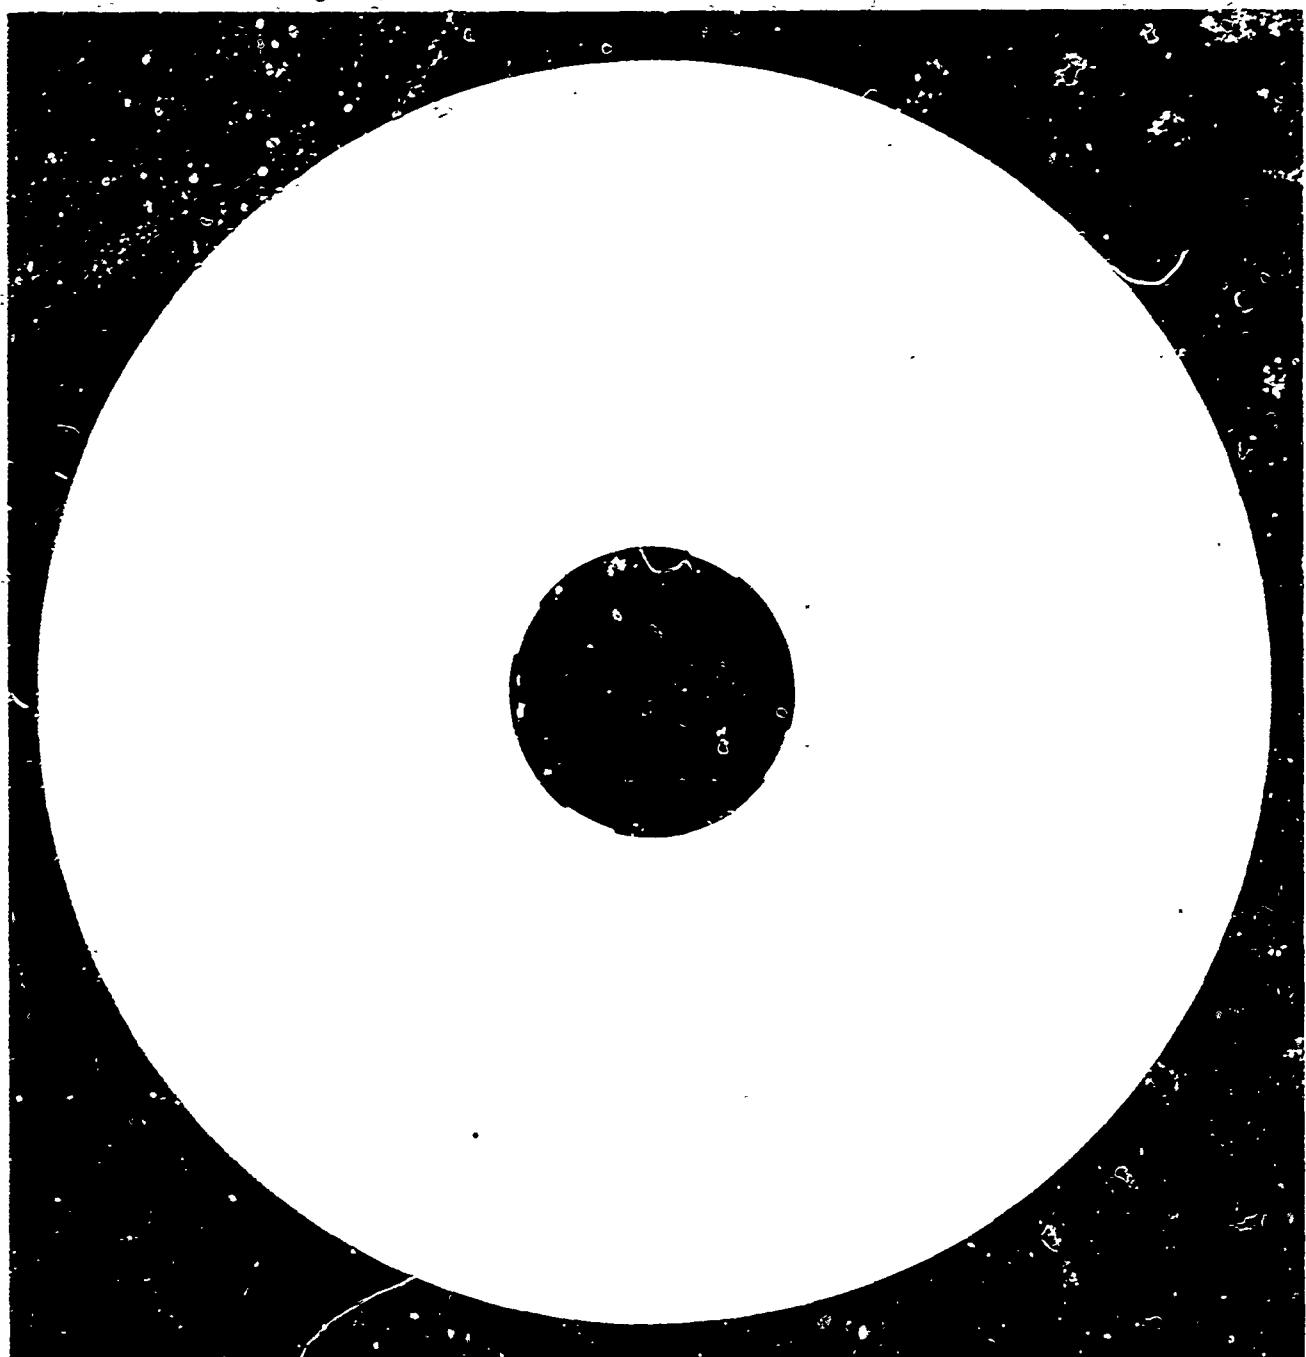


5X

20 Glycerine-20 HCl-10 HNO₃

8E927

Heat Treatment: 2150 F-4 hours-air cool
1975 F-4 hours-air cool
1550 F-25 hours-air cool
1440 F-16 hours-air cool

FIGURE 17 Transverse Section of Heat-Treated
Udimet 700 Gun Barrel Sample 376

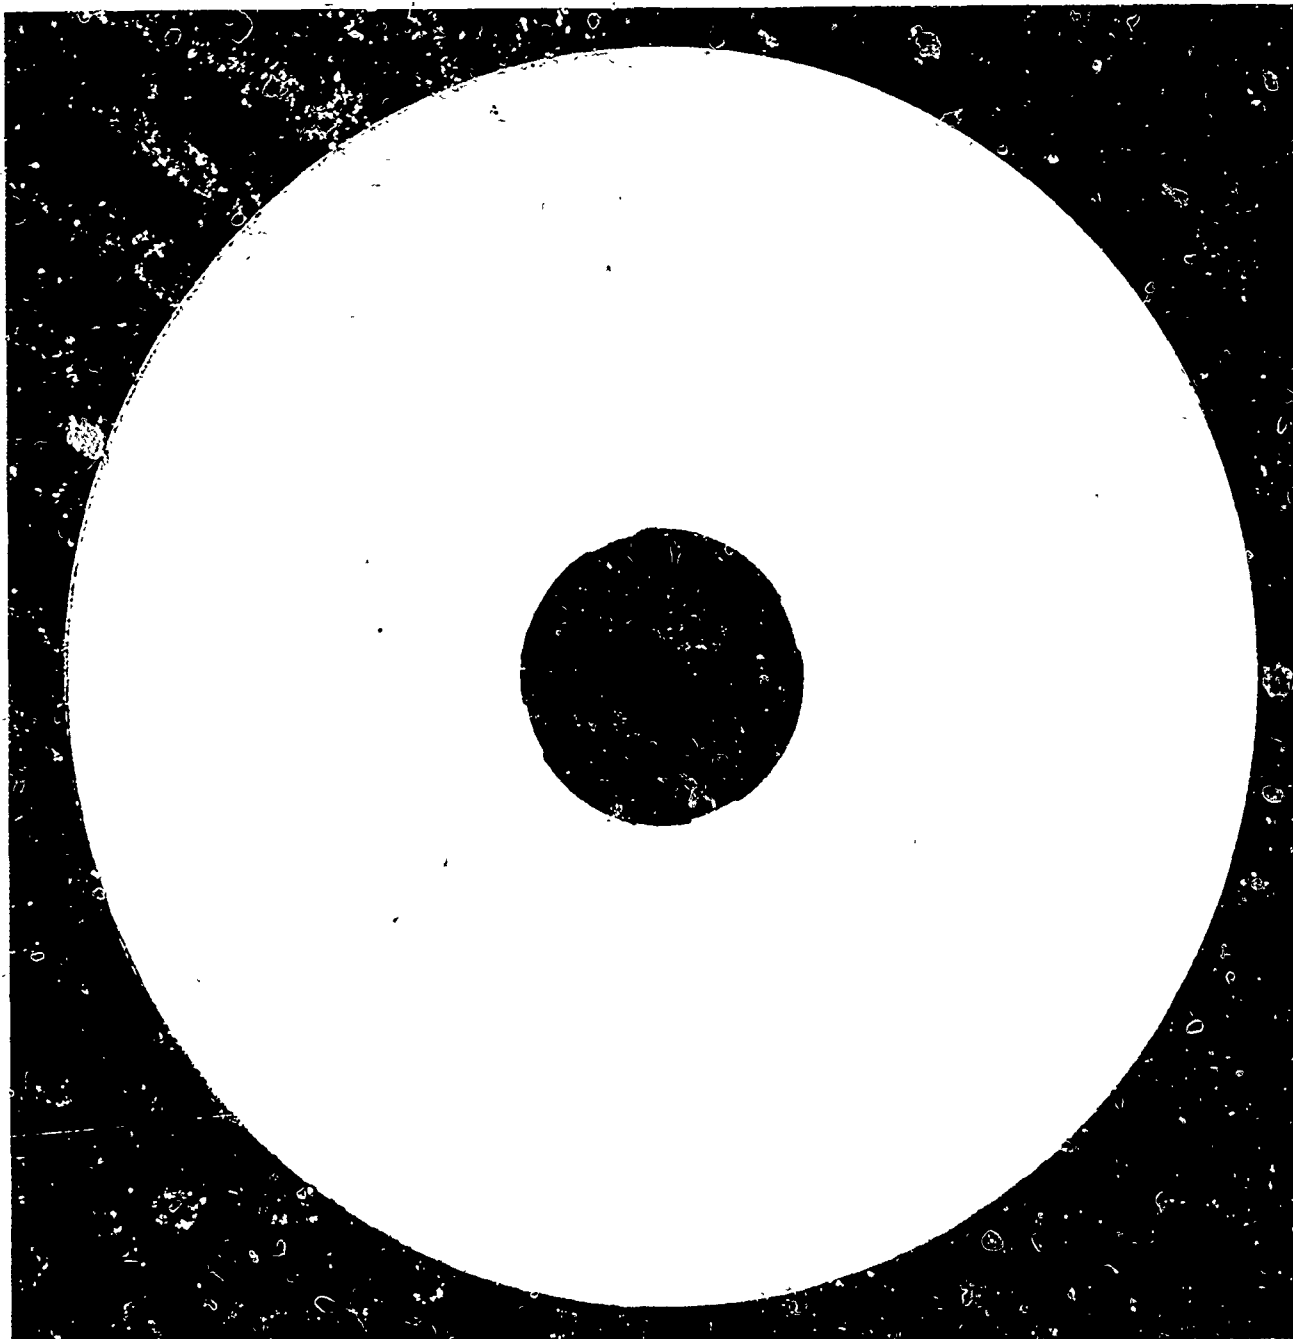


5X

20 Glycerine-20 HCl-10 HNO₃

8E928

Heat Treatment: 1875 F-1-1/2 hours-oil quench
1450 F-16 hours-air cool
1200 F-16 hours-air cool

FIGURE 18 Transverse Section of Heat-Treated
Crucible CG-27 Gun Barrel Sample 452

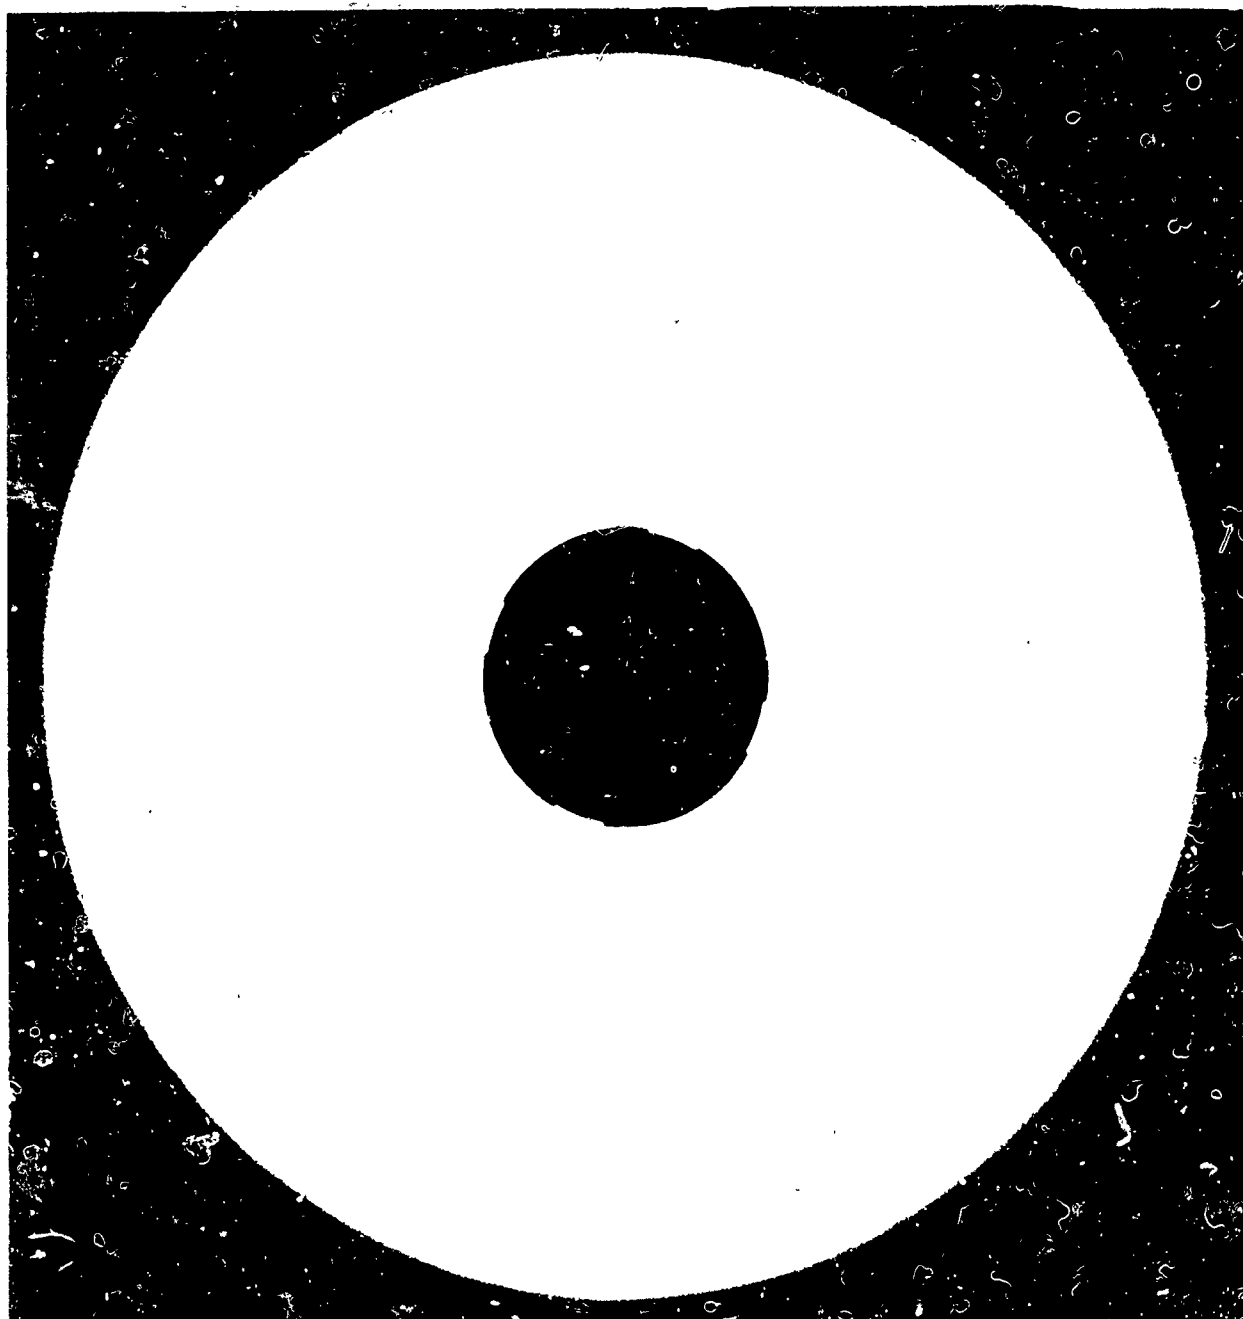

5X

40 HCl-10 HNO₃

8E926

FIGURE 19 Transverse Section of As-Swaged
Armco 21-6-9 Gun Barrel Sample 226

TABLE IX BORE DIMENSIONS OF GUN BARRELS

Alloy	Sample Number	As Swaged		After Heat Treatment (a)	
		Between Lands (b)	Diameter, inch	Between Lands (b)	Diameter, inch
Inconel 718	126	0.3016 0.3016	0.3091 0.3091	0.3000 0.3005	0.3086 0.3080
Armco 21-6-9	226	0.3007 0.3009	0.3082 0.3087	Not heat treated	
Udimet 700	376	0.3018 0.3016	0.3087 0.3091	0.3004 0.3005	0.3080 0.3080
Crucible CG-27	452	0.3018 0.3018	0.3098 0.3096	0.3014 0.3011	0.3089 0.3088

(a) Sample 126: 1800 F - 1-1/2 hr - air cooled + 1325 F - 8hr - furnace cooled to 1150 F, held at 1150 F - 8 hr - air cooled.

Sample 376: 2150 F - 4 hr - air cooled + 1975 F - 4 hr - air cooled + 1550 F - 25 hr - air cooled + 1440 F - 16 hr - air cooled.

Sample 452: 1875 F - 1-1/2 hr - oil quenched + 1450 F - 16 hr - air cooled + 1200 F - 16 hr - air cooled.

(b) Diameter measurements were made at two positions, 90 degrees apart.

Hardness Studies

Hardness determinations were made on the same transverse metallographic samples before and after heat treatment to eliminate any possible differences caused by use of different samples. Five Vickers hardness measurements were taken on the as-swaged samples along each of four radial traverses which were about 45 degrees apart. The hardness impressions were about 100 mils apart.


To determine hardness differences across much smaller distances required Knoop microhardness measurements of the samples in the as-swaged condition and after heat treatment. These hardness surveys were conducted along two radial traverses: one was started at a land and the other was started at a groove. In addition, circumferential traverses were made along a groove and a land approximately 1 mil from the surface of the bore.

Hardness data for the gun barrel samples before and after heat treatment are presented in Tables X and XI, and in Figures 20 through 23. A log scale was used for plotting the distance in the figures to show the complete traverse, while the first six readings close to the bore were clearly depicting.

The Vickers hardness data in Table X show that the hardnesses of all gun barrel blank samples were very high. A comparison of the data in Table IV on the gun barrel blanks with the data in Table X for the as-swaged samples shows that swaging increased the average hardness 72 VHN points for Inconel 718, 97 points for Armco 21-6-9, 124 points for Udimet 700, and 106 points for Crucible CG-27. Furthermore, the data indicate that the hardnesses of all alloys tend to be lower near the bore and to become progressively higher toward the OD.

Knoop hardness data in Table XI and in Figures 20 through 23 show that the average hardnesses of the as-swaged blank samples were very high. The hardnesses were as follows:

<u>Alloy</u>	<u>Average Knoop Microhardness, 100 g. Load</u>
Inconel 718	498
Armco 21-6-9	378
Udimet 700	629
Crucible CG-27	554

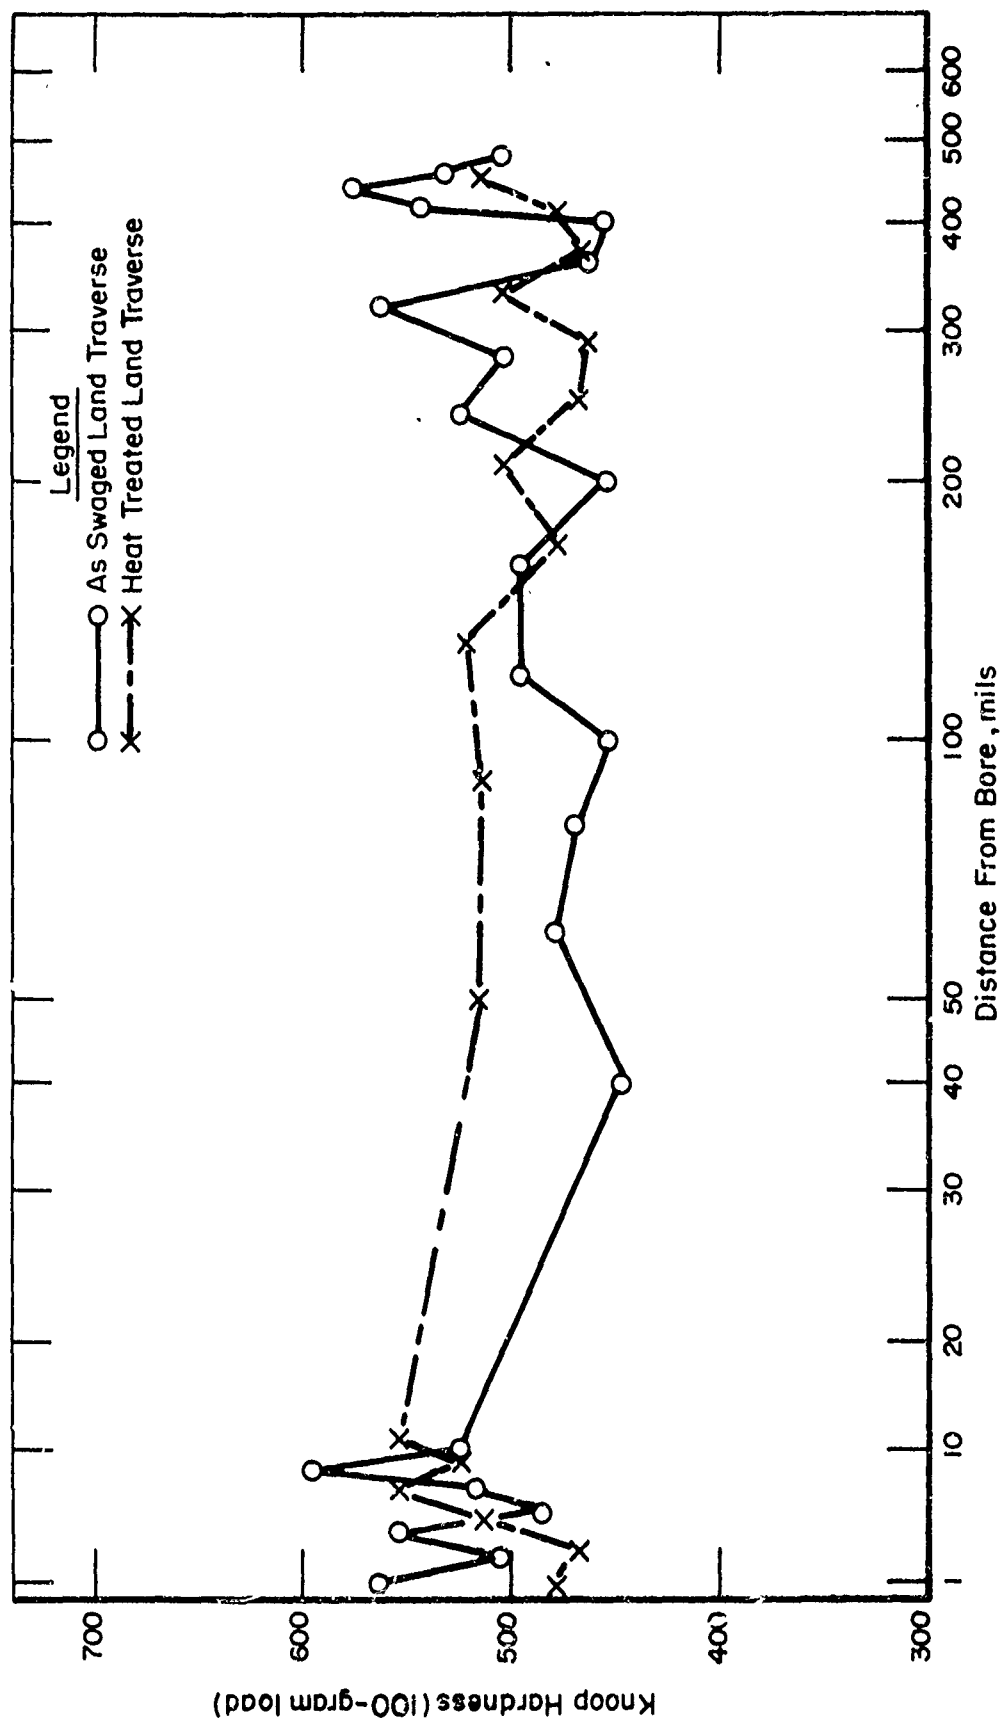

Heat Treatment: 1800 F - 1-1/2 hr - air cool + 1325 F - 8 hr,
furnace cool to 1150 F, 1150 F - 8 hr - air cool.

FIGURE 20 Knoop Hardness of Inconel 718 Gun Barrel Sample 126

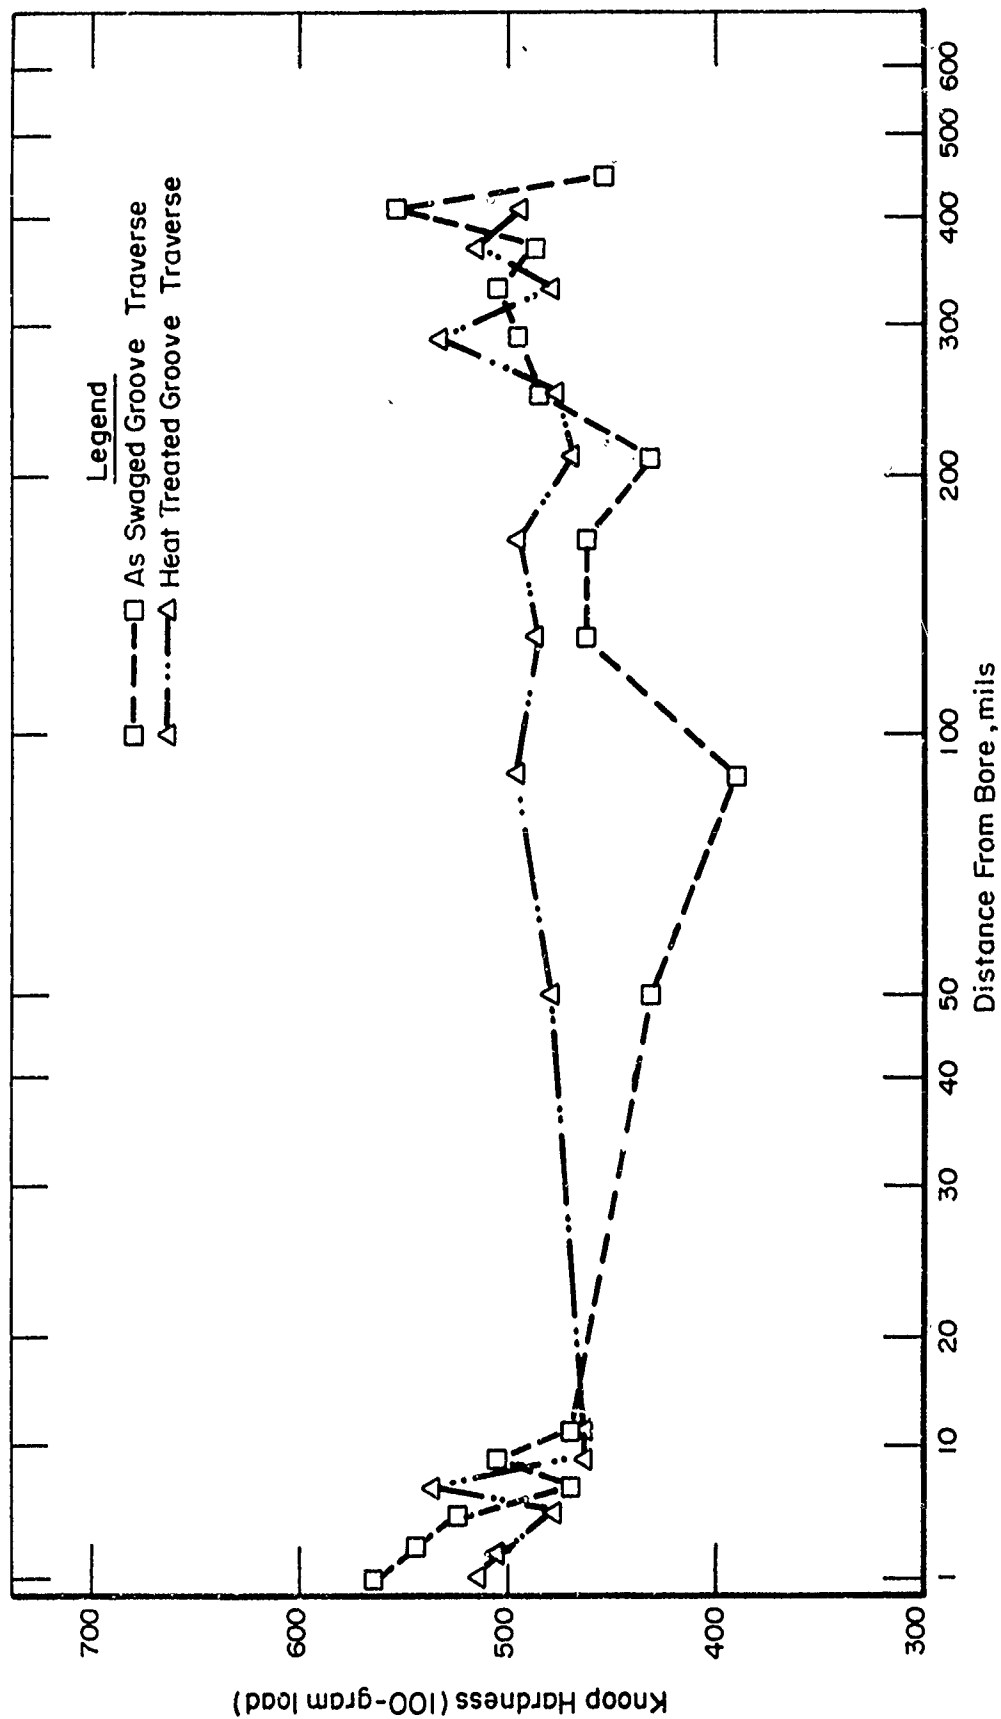


FIGURE 20 (Continued)

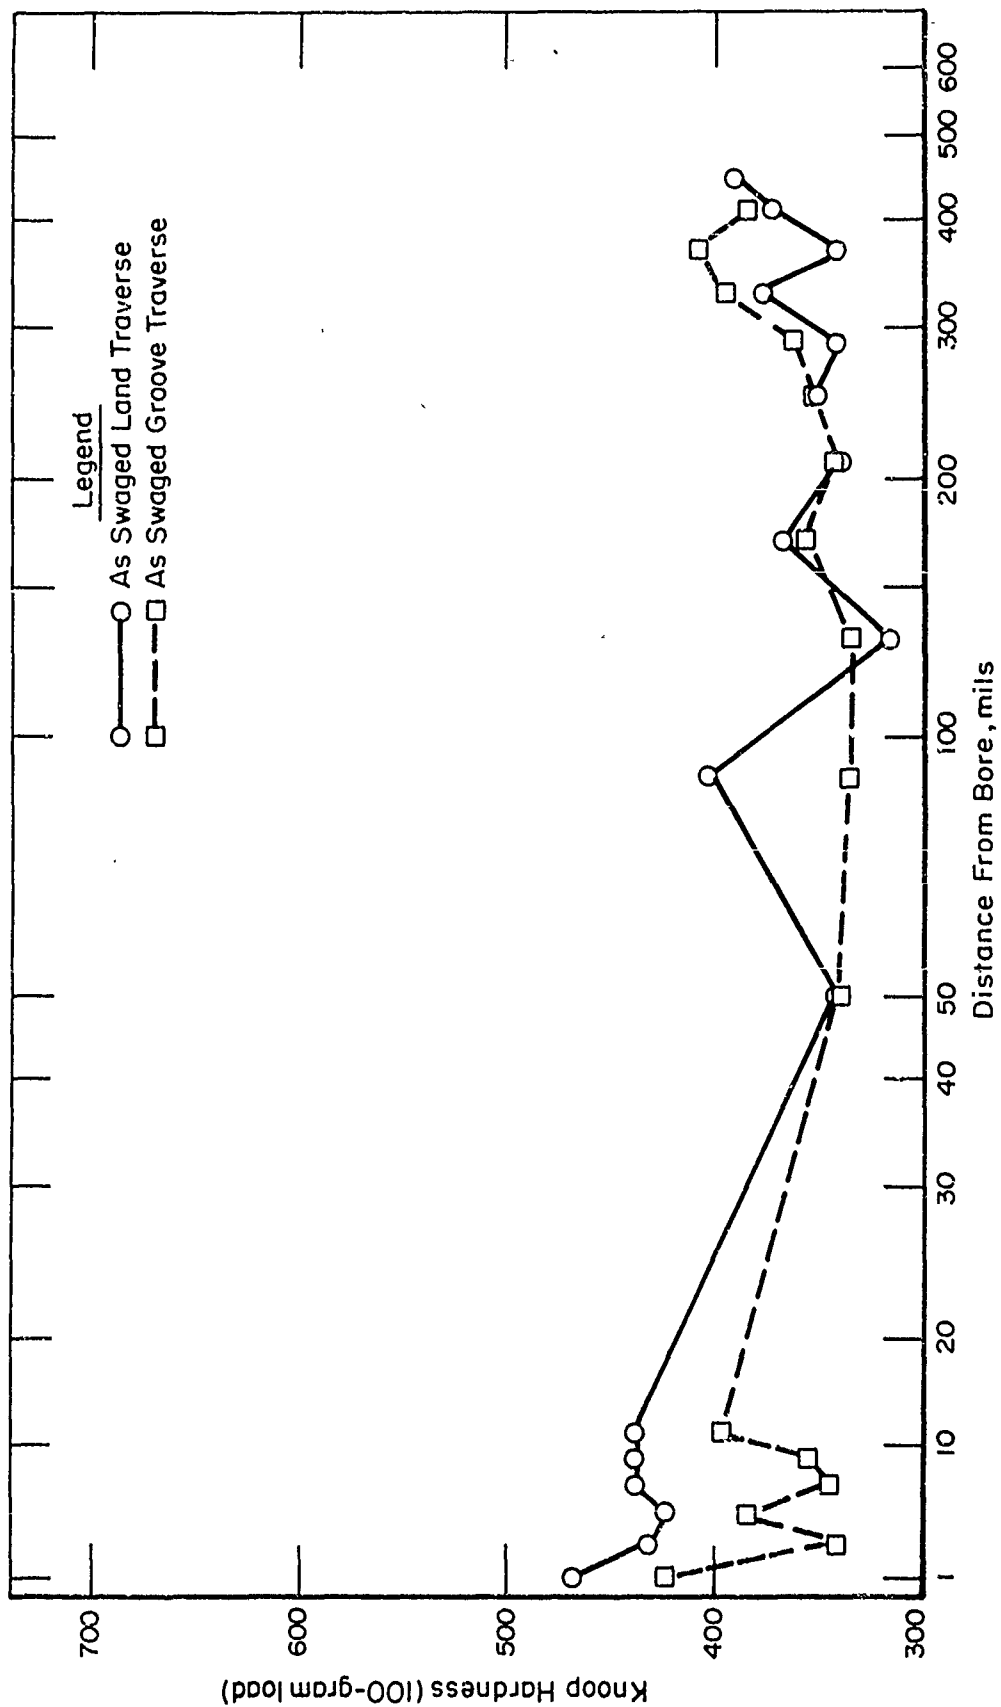


FIGURE 21 Knoop Hardness of Armco 21-6-9 Gun Barrel Sample 226

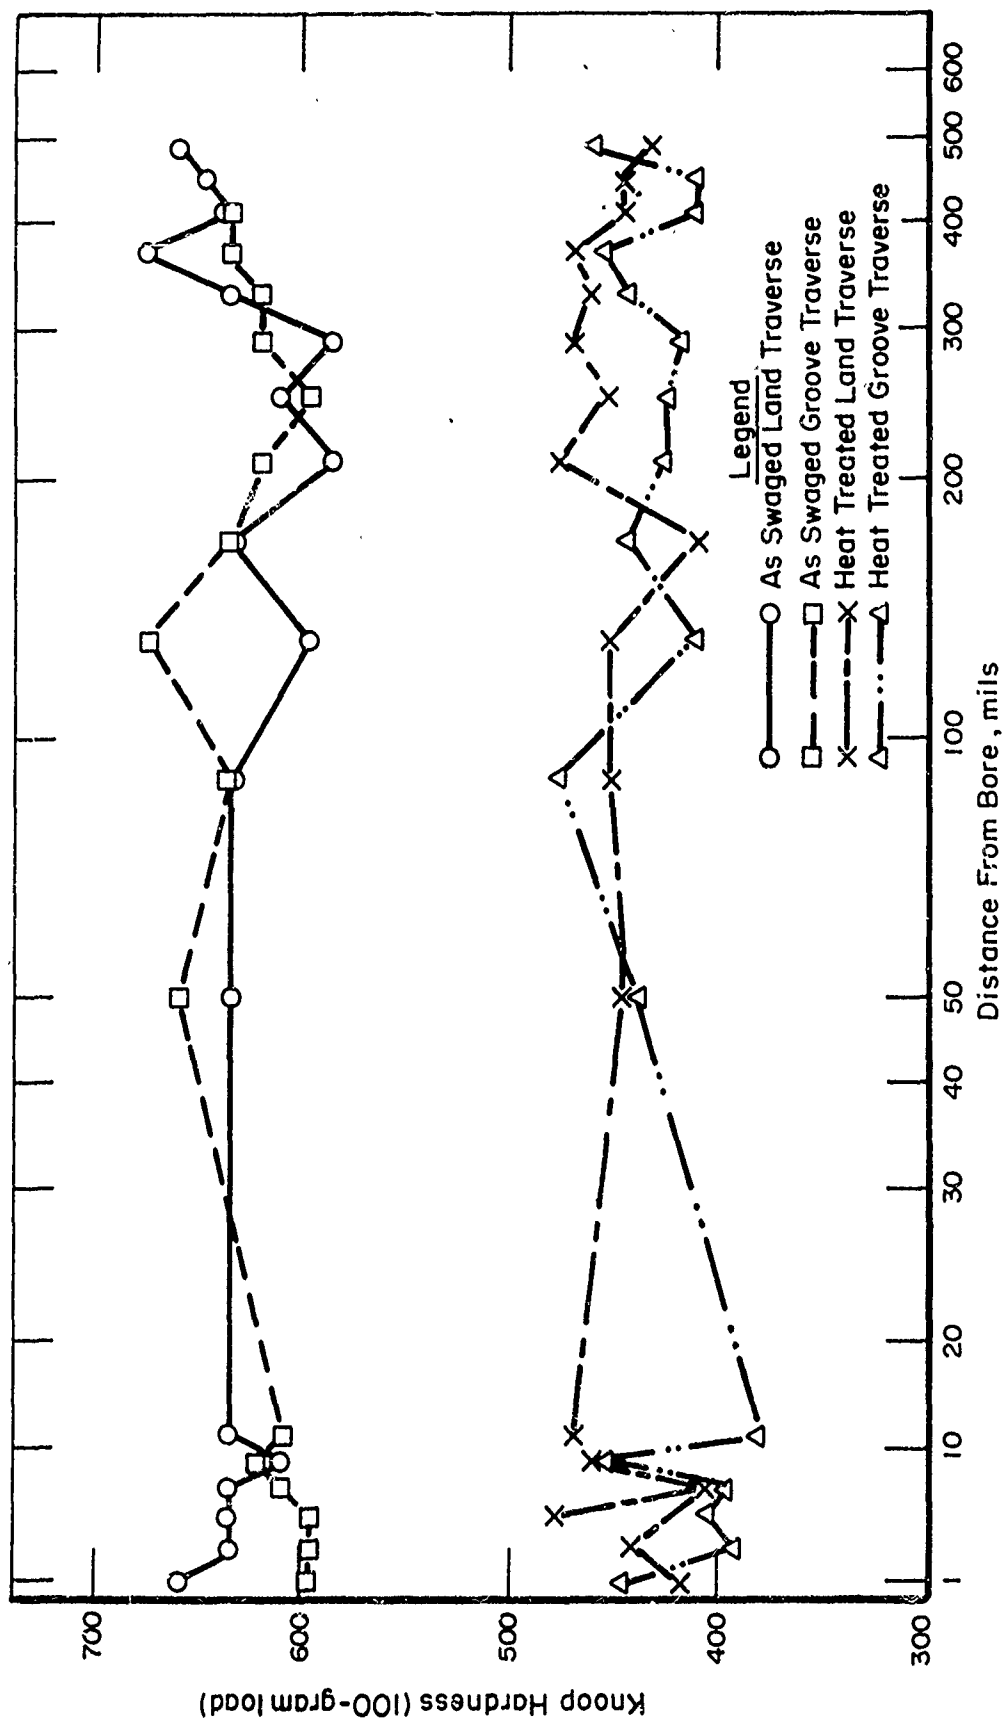


FIGURE 22 Knoop Hardness of Udimet 700 Gun Barrel Sample 376

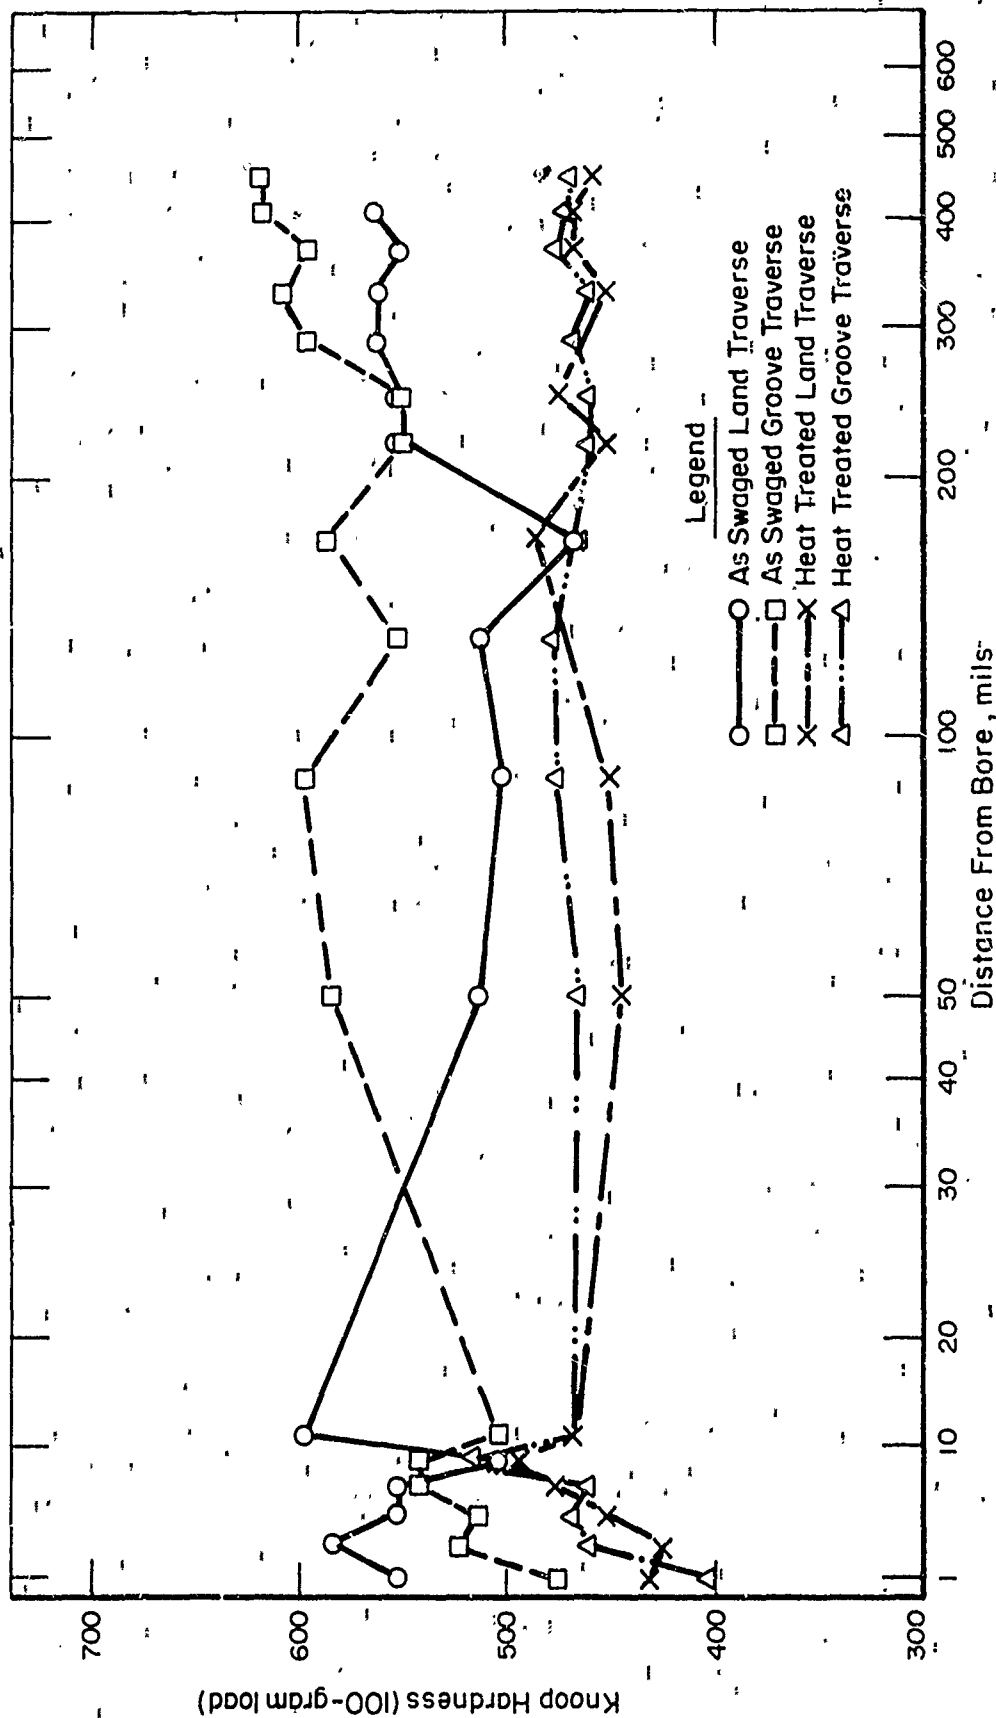


FIGURE 23 Knoop Hardness of Crucible CG-27 Gun Barrel Sample 452

TABLE X VICKERS HARDNESS OF TRANSVERSE SECTIONS OF AS-SWAGED GUN BARRELS

Alloy (a)	Location (b) of Hardness Impressions	Hardness, VHN (10-kg Load)									
		Distance From ID, mils								Overall	
		85	185	285	385	435	Average (c)	Range	Average (c)		
Inconel Alloy 718 (126)	1	357	366	376	380	390	374 (39)	330-390	364 (38)		
	2	360	357	360	380	383	368 (39)				
	3	357	357	387	380	373	370 (39)				
	4	336	330	363	345	345	344 (36)				
Armco Alloy 21-6-9 (226)	1	312	299	327	336	339	323 (34)	281-339	306 (32)		
	2	283	281	283	294	297	287 (29)				
	3	283	294	304	333	322	307 (32)				
	4	296	283	314	317	325	307 (32)				
Udimet 700 (376)	1	498	483	525	548	548	520 (50.5)	483-572	529 (51)		
	2	536	536	554	566	548	548 (52)				
	3	514	514	514	530	536	521 (50.5)				
	4	493	498	525	548	572	527 (51)				
Crucible Alloy CG-27 (452)	1	450	429	450	442	-	442 (45)	417-493	448 (46)		
	2	464	459	468	478	464	467 (47)				
	3	437	442	455	429	493	451 (46)				
	4	425	417	437	428	455	432 (44)				

(a) Sample number in parenthesis.

(b) The hardness impressions were taken along four radial traverses which were about 45 degrees apart.

(c) Numbers in parentheses are Rockwell C hardness numbers converted from the Vickers numbers. The Rockwell C hardness numbers are for reference only, since the accuracy of the conversion is not known.

TABLE XI SUMMARY OF KNOOP MICROHARDNESS DATA ON GUN BARREL SAMPLES
IN THE AS-SWAGED CONDITION AND AFTER HEAT TREATMENT

Alloy	Sample Number	Knoop Microhardness, 100g Load					
		Land Traverse		Groove Traverse		Overall	
		Range	Average	Range	Average	Range	Average
<u>As Swaged</u>							
Inconel 718	126	446-596	508	392-563	484	392-598	498
Armco 21-6-9	226	317-470	388	336-425	367	317-470	378
Udimet 700	376	586-675	630	597-675	624	586-688	629
Crucible CG-27	452	470-597	544	477-620	563	440-620	554
<u>Heat Treated</u>							
Inconel 718	126	463-554	501	469-533	492	462-565	496
Armco 21-6-9	226	-	-	-	-	-	-
Udimet 700	376	400-470	450	392-478	428	380-478	438
Crucible CG-27	452	425-495	461	404-514	467	374-514	464

Furthermore, data show that the average Knoop microhardness of Inconel 718, Udimet 700, and Crucible CG-27 decreased rather than increased after heat treatment. Udimet 700 decreased 191 points, while that of Crucible CG-27 decreased 90 points.

The hardness curves for Inconel 718 and for Udimet 700 shown in Figures 20 and 22 indicate that no significant trend occurred in hardness across land and groove traverses of the samples in the as-swaged condition and after heat treatment.

The curve in Figure 23 for Crucible CG-27 indicates that the hardness of the sample in the as-swaged and in the heat-treated condition is lowest near the bore and becomes progressively higher toward the OD.

The curve in Figure 21 for Armco 21-6-9 indicates that the hardness of the as-swaged sample is highest near the bore and becomes progressively lower toward the OD.

Fifteen high-quality experimental 7.62mm gun barrel blanks of the four alloys were selected for evaluation. The gun barrels selected according to number, alloy, and rated quality are identified in Table XII. As mentioned previously, the quality was based on straightness and on borescopic examination.

Good rifling starts approximately 3/4 inch from the swaged end and approximately 1-1/4 inches from the unswaged end of each gun barrel blank. However, these distances are approximate and must be measured on each blank.

Test Firing and Analysis of Rotary-Swaged Barrels

As part of a comprehensive program, 7.62mm gun barrels were made of Crucible CG-27 alloy by drilling and cold swaging, and by pierce-extruding and cold swaging. Barrels of both M60 and M134 configurations were test-fired in the unplated and chrome-plated conditions. Barrels were also made of fine-grained CG-27 produced by thermomechanical treatment and by powdermetallurgy techniques. The results of this intensive investigation giving details of fabrication and the evaluation of material and service performance will be presented in a separate report.

**TABLE XII. IDENTIFICATION AND QUALITY RATING OF
EXPERIMENTAL 7.62MM GUN BARREL BLANKS**

Gun Barrel	Alloy	Quality Rating^(a)
11	Inconel 718	4
13	Inconel 718	2
14	Inconel 718	3
15	Inconel 718	1
21	Araco 21-6-9	1
23	Araco 21-6-9	3
24	Araco 21-6-9	4
25	Araco 21-6-9	2
31	Udimet 700	3
32	Udimet 700	5
34	Udimet 700	2
35	Udimet 700	4
38	Udimet 700	1
44	Crucible CG-27	1
45	Crucible CG-27	2

(a) A rating of (1) indicates the blank with the highest quality for the particular alloy.

The cold swaged barrel blanks of the selected nickel-base alloys were completely heat treated to develop optimum mechanical properties. These superalloys, Inconel 718 and Udimet 700, together with swaged blanks of the iron-base alloy, Armco 21-6-9, were then finish-machined to the drawing requirements of the M60 machine gun barrel. The barrels of these alloys were subjected to severe test-firing schedules and then metallurgically examined.

Typical solution treatments and aging cycles were applied to these alloys. Swaged blanks of Inconel 718 were solution-treated and aged. After each heat treatment, the blanks were cooled to room temperature, in the furnace, by influent helium.

Solution treatment - 1 hour at 1800°F.

Aging treatment - 8 hours at 1325°F, furnace cooled approximately 100°F/hour to 1150°F, held 8 hours at 1150°F.

Swaged blanks of Udimet 700 were solution-treated, stabilized, and double aged. These barrel blanks were also cooled by helium after each heat treatment.

Solution treatment - 4 hours at 2150°F.

Stabilization treatment - 4 hours at 1975°F.

Aging treatments - 25 hours at 1550°F, and 16 hours at 1440°F.

After the complete heat treatments, no distortion was observed in the bore along the length of the blanks, even though the swaged tubes were horizontally positioned in the heat-treat furnace. Chemical analysis before and after heat treatment indicates no loss of alloying elements in the materials.

The barrel blanks of the nonheat-treated Armco 21-6-9 alloy and the heat-treated nickel-base alloys were finish-machined to the drawing requirements of the M60 gun barrel, Rock Island Arsenal Drawing 140241.

The completed gun barrels of the Armco 21-6-9, Inconel 718, and Udimet 700 alloys were subjected to the following test-firing schedule:

Fire six 125-round bursts with 10-second cooling between bursts; air cool to room temperature. Continue this schedule until the barrel exceeds velocity, accuracy or yaw limits, or is otherwise considered unserviceable.

Check for velocity, accuracy, and yaw at the start of the program, after the first 3000 rounds, and after every 750 rounds.

Test-firing results obtained from this schedule are given in Table XIII.

TABLE XIII. 7.62MM M60 BARREL LIFE - FIRING SCHEDULE I

<u>Test Barrel Material</u>	<u>Total Rounds Fired</u>	<u>Limits Exceeded</u>
Armco 21-6-9	6000	Accuracy and yaw
Inconel 718	8600	Yaw
Udimet 700	9800	Yaw

The following more severe firing schedule was imposed on additional swaged and heat-treated gun barrels of Inconel 718 and Udimet 700:

Fire four 300-round bursts with 10-second cooling between bursts; air cool to room temperature. Continue this schedule until the barrel exceeds velocity, accuracy or yaw limits, or is unserviceable.

Check for velocity, accuracy, and yaw at the start of the program and after every 1200 rounds.

The test firing results are given in Table XIV.

TABLE XIV. 7.62MM M60 BARREL LIFE - FIRING SCHEDULE II

<u>Test Barrel Material</u>	<u>Total Rounds Fired</u>	<u>Limits Exceeded</u>
Inconel 718	3600	Accuracy and yaw
Udimet 700	5000	Accuracy and yaw

Sufficient heat was generated during each burst of the test-firing schedule to produce a dull red glow along the entire length of the barrel surface.

On the bore surface of the test-fired Armco 21-6-9 alloy barrel, extensive deterioration of the rifling and intergranular cracking along the entire rifle length can be observed. A view of the bore near the chamber end of the barrel is given in Figure 24. Microscopic examination of sections of the bore reveals complete elimination of the lands, sharp intergranular cracks extending approximately 0.005 to 0.010-inch beneath the bore surface, and erosion by grain removal. Cracking and erosion of the bore near the origin of rifling are shown in Figure 25.

Bore replicas of each test-fired nickel-base alloy barrel reveal appreciable deterioration of the rifling, originating about 6 to 8 inches from the chamber end and extending to the muzzle end. A comparison can be made of the rifling near the chamber and muzzle ends of the bore from the replicas shown in Figures 26 and 27.

Examination of the test-fired Inconel 718 alloy barrels near the origin of rifling reveals blunt, intergranular, radial cracks originating along land-groove junctions and across land surfaces. This erosive condition of the land near the chamber end of the bore is shown in Figure 28. Three of the four lands near the muzzle end of each barrel are completely eroded. The fourth land, Figures 29 and 30, has retained the rifling contour on its lead side where much friction is produced by contact with advancing projectiles.

Long, sharp, intergranular cracks occurred at the bore surface near the origin of rifling of the test-fired Udimet 700 alloy barrels. Similar to Inconel 718 alloy barrels, these cracks start in land-groove junctions and grain boundaries across the land surface. Land projection on the lead side and long cracks, which have become transgranular as they penetrate further beneath the bore surface, are shown in Figures 31 and 32. Near the muzzle end in the bore of the barrel test fired in Schedule I, a smooth even wear occurred which is shown in Figure 33 along with the lead side of the single remaining land. In contrast, the severe erosion by grain removal in the same area of the Schedule II barrel is illustrated in Figure 34. All lands have been completely eliminated.


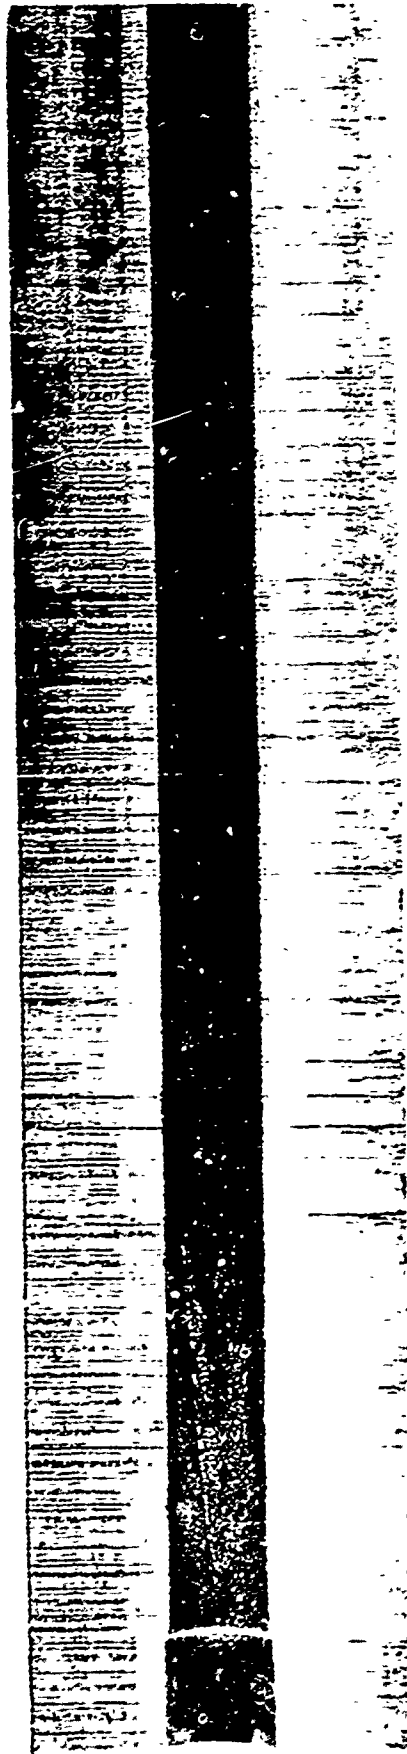


FIGURE 24 Longitudinal Section of Bore Near Chamber End of
21-6-9 Alloy M60 Gun Barrel after 6000 Rounds
Schedule I.



100X

FIGURE 25 Transverse Section of Bore,
 1/2 Inch From Chamber, of the 21-6-9
 Alloy M60 Gun Barrel after 6000 Rounds
 Schedule I.

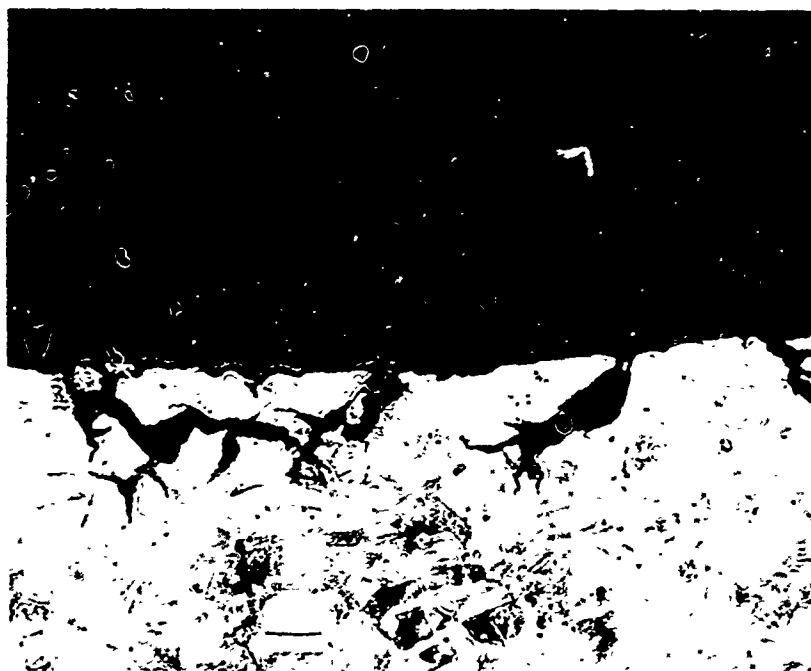

(a) Chamber End




(b) Muzzle End

FIGURE 26 Replicate of Bore of Test-Fired Inconel 718 Alloy
M60 Gun Barrel after 8600 Rounds
Schedule I.




(a) Chamber End

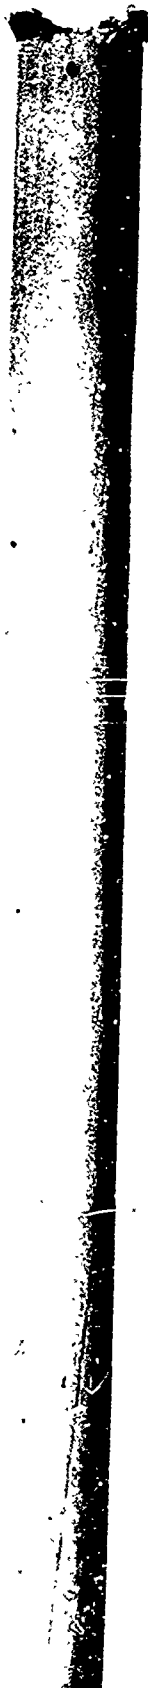

(b) Muzzle End

FIGURE 27 Replicate of Bore of Test-Fired Udimet 700 Alloy
M60 Gun Barrel after 9800 Rounds
Schedule I.

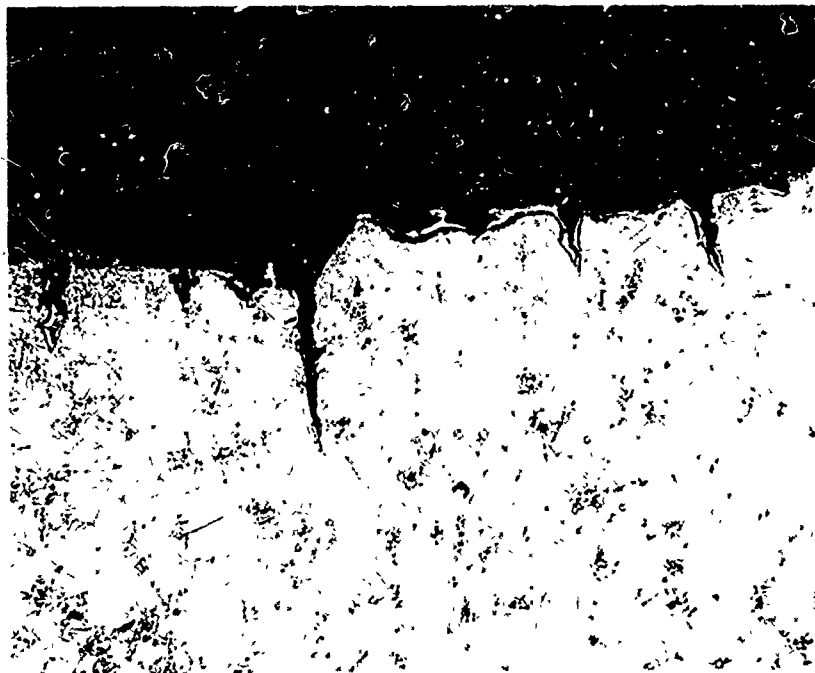

100X

FIGURE 28 Transverse Section of Bore,
 2 Inches From Chamber, of
Inconel 718 Alloy M60 Gun Barrel after 8600 Rounds
 Schedule I.



100X

Reproduced from
best available copy.

FIGURE 29 Transverse Section of Bore,
 1 Inch From Muzzle End, of
Inconel 718 Alloy M60 Gun Barrel after 8600 Rounds
 Schedule I.




1.00X

FIGURE 30 Transverse Section of Bore,
1 Inch From Muzzle End, of
Inconel 718 Alloy M60 Gun Barrel after 3600 Rounds
Schedule II.



100X

FIGURE 31 Transverse Section of Bore,
 2 Inches From Chamber, of
Udimet 700 Alloy M60 Gun Barrel after 9800 Rounds
 Schedule I

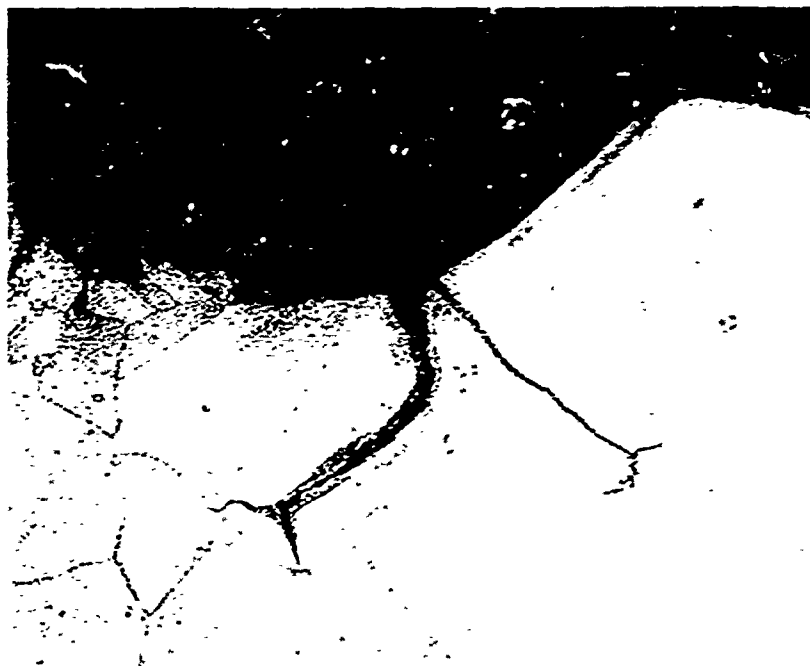

400X

FIGURE 32 Transverse Section of Bore,
1-1/2 Inches From Chamber, of
Udimet 700 Alloy M60 Gun Barrel after 9800 Rounds
Schedule I



400X

FIGURE 33 Transverse Section of Bore,
 1 Inch From Muzzle End, of
Udimet 700 Alloy M60 Gun Barrel after 9800 Rounds
 Schedule I.



400X

FIGURE 34 Transverse Section of Bore,
 1 Inch From Muzzle End, of
 Udimet 700 Alloy M60 Gun Barrel after 5000 Rounds
 Schedule II.

Barrels made of both Inconel 713 and Udimet 700 were retired from test firing because of excessive yaw. This yaw is directly attributable to the wearing away of the lands near the muzzle end of the barrel. In spite of cracks, which form in the material, both Inconel 712 and Udimet 700 show excellent resistance to breech-end erosion. Of the two, Udimet 700 has a higher resistance to the environment imposed by rapid-fire weapons.

CONCLUSIONS

The following conclusions are based on the results of this study to produce 7.62mm rifled gun barrels from three high-temperature alloys and a stainless steel by cold swaging:

1. High-quality 7.62mm rifled gun barrel blanks of the four selected alloys - Inconel 718, Armco 21-6-9, Udimet 700, and Crucible CF-27 - can be produced by cold swaging in much shorter times than by conventional machining.
2. The recommended heat treatments for the alloys can be successfully performed on full-length as-swaged barrel blanks. Chemical analysis both before and after heat treatment indicated no loss of alloying elements.
3. The high degree of configurational integrity and the surface finish of the rifled bore are additional advantages of rotary swaging.
4. With the use of rotary-swaging techniques to produce rifling contours in tubes of high-strength materials, the use of erosion-resistant materials for rapid-fire gun barrels is feasible.

LITERATURE CITED

1. Collins, Lawrence, W., Jr., "Inside Chipless Machining," Machinery, 122-125 (December, 1960).
2. Dallas, Daniel B., "Cold Forming by Multiflow," ASTM Vectors, 2, (4), 22-25 (November, 1967).
3. Daniels, Harold R., "The New Shape of Swaging," Metalworking, 77-80, (July, 1956).
4. "Extruded Gun Barrels Blast Material Costs," Steel (May 9, 1966).
5. "Hot and Cold Forging of Gun Barrels on G.F.M. Machines," Machinery, London (November 15, 1957).
6. "Rotary Swaging of Bars and Tubes," Metals Handbook - Forming, 8th Edition, 4, American Society for Metals, Cleveland, Ohio, 333-346 (1969).
7. Strohecker, Daniel E., "Swaging," Metal Deformation Processing, Volume III, DMIC Report 243, Defense Metals Information Center, Battelle Memorial Institute, Columbus, Ohio, 104-116, (June 10, 1967).
8. Strohecker, Daniel E., "Swaging Today," The Tool and Manufacturing Engineer (May, 1968).
9. Wick, Charles H., Chipless Machining, The Industrial Press, New York (1960) "Internal Swaging, Radial Forging, and Cold Forming of Multiple-Diameter Shafts," 229-256.

APPENDIX A

DATA SHEETS FOR THE COLD SWAGING OF GUN BARRELS

TABLE A-1. GOLD SWAGING DATA SHEETS FOR GUN BARRELS

Barrel No.:	37	38	35	34	33	31	22
Material	Udimate 700	Udimate 700	Udimate 700	Udimate 700	Udimate 700	Armedo 21-6-9	Armedo 21-6-9
Barrel OD, in. Length, in.	1.330 25-1/8	1.313 26-1/8	1.312 26-1/4	1.312 26-1/4	1.312 26-5/16	1.278 27-9/16	1.307 26-5/16
Blank OD, in. ID, in. Length, in.	1.503	1.503	1.503	1.502	1.504	1.500	1.500
Feed, in./min.	20	20	20	20	20	20	20
	15	15	15	15	15	15	15
Wedges Shim, in.	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004
Wedge Position Dial	550	530	530	530	530	530	560
Rotation, rpm	130	130	130	130	130	130	130
Back Pressure, psi	300	400	400	400	400	400	400
Cushion Pressure, psi	800	800	800	800	800	800	800
Mandrel No.	1	1	1	1	1	1	1
Mandrel Forward Position, in.	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8

TABLE A-1. (Continued)

Barrel No.:	23	24	25	15	14	11	12
Material	Armeo 21-6-9	Armeo 21-6-9	Armeo 21-6-9	Inconel 718	Inconel 718	Inconel 718	Inconel 718
Barrel OD, in.	1.307	1.307	1.307	1.286	1.286	1.274	1.263
Length, in.	26-1/4	26-5/16	26-5/16	26-5/16	26-3/8	26-1/2	26-3/8
Blank OD, in.	1.500	1.500	1.500	1.475	1.477	1.465	1.450
ID, in.	20	20	20	20	20	20	20
Length, in.	15	15	15	15	15	15	15
Feed, in./min.	15	15	15	15	15	15	15
Wedges Shim, in.	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004	A 0.003 C 0.004
Wedge Position Dial	560	560	560	530	530	520	510
Rotation, rpm	130	130	130	130	130	130	130
Back Pressure, psi	400	400	400	400	400	400	400
Cushion Pressure, psi	800	800	800	800	800	800	800
Mandrel No.	1	1	1	1	1	1	1
Mandrel Forward Position, in.	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8

TABLE A-1. (Continued)

Barrel No.:	13	41	32	31	42	43	44	45
Material	Inconel 718	Crucible CG-27	Udimet 700	Udimet 700	Crucible CG-27	Crucible CG-27	Crucible CG-27	Crucible CG-27
Barrel OD, in.	1.260	1.319	1.313	1.314	1.311	1.311	1.303	1.303
Length, in.		26	26-3/16	26-3/16	26-3/8	26-3/8	26-5/8	26-5/8
Blank OD, in.	1.445	1.504	1.500	1.500	1.500	1.504	1.505	1.504
ID, in.								
Length, in.	20	20	20	20	20	20	20	20
Feed, in./min.	15	15	15	15	15	15	12	12
Wedges Shim, in.	A 0.003 C 0.004	A 0.003 C 0.004	A 0.004 C 0.004	A 0.004 C 0.004	A 0.004 C 0.004	A 0.004 C 0.004	A 0.008 C 0.008	A 0.008 C 0.008
Wedge Position Dial	505	550	530	530	540	540	540	540
Rotation, rpm	130	130	130	130	130	130	105	105
Back Pressure, psi	400	400	400	400	400	450	450	450
Cushion Pressure, psi	800	800	800	800	800	800	800	800
Mandrel No.	1	1	2	2	2	2	2	2
Mandrel Forward Position, in.	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8	2-5/8

APPENDIX B

DIAMETER AND STRAIGHTNESS DATA
COLD-SWAGED GUN BARRELS

APPENDIX B

DIAMETER AND STRAIGHTNESS DATA COLD-SWAGED GUN BARRELS

The diameters of the swaged gun barrels were measured with a micrometer at distances of 1-1/2, 8-1/2, 15-3/8, and 22-3/8 inches from the end of the barrel. Two measurements, 90 degrees apart, were taken at the four locations to determine the degree of out-of-roundness. The diameter measurements are given in Table B-1.

The straightness of the swaged gun barrels was measured by means of a dial indicator. The gun barrels were placed in a lathe and the indicator was moved along the length of the barrel in four traverses 90 degrees apart. Readings were taken along the traverses at distances of 1-1/2, 8-1/2, 15-3/8, and 22-3/8 inches from one end of the barrel. The indicator readings are given in Tables B-2 through B-5. The first indicator reading was taken as the zero point. The total indicator reading (TIR) is given for each traverse.

TABLE B-1. DIAMETER MEASUREMENTS TAKEN ON AS-SWAGED GUN BARRELS

Alloy	Barrel Number	Diameter (a) (in inches) at Indicated Distance From End of Barrel					
		1-1/2 inches		8-1/2 inches		15-3/8 inches	
		A	B	A	B	A	B
Inconel 718	11	1.273	1.273	1.273	1.272	1.272	1.272
	12	1.263	1.262	1.262	1.262	1.262	1.261
	13	1.260	1.260	1.258	1.259	1.258	1.257
	14	1.286	1.286	1.286	1.286	1.285	1.285
	15	1.287	1.287	1.286	1.286	1.285	1.285
Armeo 21-6-9	21	1.278	1.278	1.277	1.277	1.277	1.276
	22	1.307	1.308	1.306	1.307	1.306	1.306
	23	1.307	1.307	1.306	1.306	1.306	1.306
	24	1.307	1.307	1.306	1.306	1.305	1.305
	25	1.307	1.307	1.307	1.306	1.305	1.305
Udimet 700	31	1.315	1.315	1.314	1.314	1.313	1.312
	32	1.313	1.313	1.312	1.312	1.311	1.311
	33	1.312	1.312	1.312	1.312	1.311	1.311
	34	1.314	1.314	1.313	1.313	1.312	1.311
	35	1.313	1.313	1.313	1.313	1.312	1.312
	37	1.331	1.330	1.331	1.331	1.330	1.331
	38	1.314	1.314	1.313	1.314	1.313	1.312
Crucible CG-27	41	1.320	1.320	1.319	1.319	1.319	1.316
	42	1.310	1.310	1.310	1.310	1.310	1.311
	43	1.309	1.309	1.309	1.309	1.309	1.310
	44	1.307	1.307	1.305	1.305	1.302	1.301
	45	1.303	1.303	1.303	1.303	1.303	1.304

(a) Positions A and B were 90 degrees apart.

TABLE B-2. STRAIGHTNESS MEASUREMENTS TAKEN ON AS-SWAGED 718 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (inch) at Indicated Distance From End of Barrel				Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.	
11	1	0.000	+0.007	+0.012	+0.005	0.012
	2	+0.001	0.000	-0.001	-0.004	0.005
	3	-0.005	-0.013	-0.018	-0.013	0.013
	4	-0.007	-0.004	-0.005	-0.005	0.003
12	1	0.000	+0.010	+0.010	+0.002	0.010
	2	+0.003	+0.018	+0.018	+0.010	0.015
	3	+0.004	-0.015	-0.022	-0.020	0.026
	4	-0.007	-0.022	-0.027	-0.025	0.020
13	1	0.000	+0.0005	+0.0015	0.000	0.0015
	2	0.000	-0.006	-0.009	-0.0075	0.009
	3	-0.004	-0.0065	-0.011	-0.011	0.007
	4	-0.004	+0.002	+0.0005	-0.003	0.006
14	1	0.000	+0.0025	-0.001	-0.002	0.0045
	2	-0.006	-0.018	-0.018	-0.011	0.012
	3	-0.007	-0.009	-0.007	-0.007	0.002
	4	-0.001	+0.010	+0.009	+0.0015	0.011
15	1	0.000	-0.002	-0.003	-0.001	0.003
	2	-0.001	+0.002	+0.0025	+0.0017	0.0035
	3	-0.002	0.000	-0.002	-0.0045	0.0045
	4	-0.001	-0.0045	-0.007	-0.007	0.006

(a) Traverses were 90 degrees apart along the length of the barrel.

(b) The value given is the difference between the maximum and minimum indicator readings along a given traverse.

TABLE B-3. STRAIGHTNESS MEASUREMENTS TAKEN ON AS-SWAGED ARMCO ALLOY 21-6-9 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (in.) at Indicated Distance From End of Barrel				Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.	
21	1	0.000	-0.003	-0.007	-0.007	0.007
	2	-0.0015	-0.006	-0.007	-0.004	0.0055
	3	-0.0005	+0.003	+0.004	+0.002	0.0045
	4	+0.002	+0.005	+0.004	0.000	0.005
22	1	0.000	-0.0025	-0.006	-0.004	0.006
	2	+0.0005	+0.001	+0.001	+0.0025	0.002
	3	+0.0002	+0.003	+0.004	+0.001	0.0038
	4	0.000	-0.001	-0.004	-0.006	0.006
23	1	0.000	-0.0005	0.000	0.000	0.0005
	2	+0.0005	+0.0025	+0.0015	-0.0015	0.004
	3	0.000	-0.001	-0.004	-0.005	0.005
	4	-0.001	-0.004	-0.0055	-0.004	0.0045
24	1	0.000	-0.002	-0.0042	-0.004	0.0042
	2	-0.001	-0.0025	-0.0035	-0.002	0.0025
	3	-0.0015	-0.001	-0.002	-0.0035	0.0025
	4	-0.001	0.000	-0.0022	-0.0055	0.0055
25	1	0.000	-0.002	-0.006	-0.006	0.006
	2	-0.0005	+0.001	-0.001	-0.003	0.004
	3	-0.00015	0.000	+0.001	0.000	0.00115
	4	-0.001	-0.003	-0.004	-0.003	0.003

(a) Traverses were 90 degrees apart along the length of the barrel.

(b) The value given is the difference between the maximum and minimum indicator readings along a given traverse.

TABLE B-3. STRAIGHTNESS MEASUREMENTS TAKEN ON AS-SWAGED ARNCO ALLOY 21-6-9 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (inch) at Indicated Distance From End of Barrel				Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.	
21	1	0.000	-0.003	-0.007	-0.007	0.007
	2	-0.0015	-0.006	-0.007	-0.004	0.0055
	3	-0.0005	+0.003	+0.004	+0.002	0.0045
	4	+0.002	+0.005	+0.004	0.000	0.005
22	1	0.000	-0.0025	-0.006	-0.004	0.006
	2	+0.0005	+0.001	+0.001	+0.0025	0.002
	3	+0.0002	+0.003	+0.004	+0.001	0.0038
	4	0.000	-0.001	-0.004	-0.006	0.006
23	1	0.000	-0.0005	0.000	0.000	0.0005
	2	+0.0005	+0.0025	+0.0015	-0.0015	0.004
	3	0.000	-0.001	-0.004	-0.005	0.005
	4	-0.001	-0.004	-0.0055	-0.004	0.0045
24	1	0.000	-0.002	-0.0042	-0.004	0.0042
	2	-0.001	-0.0025	-0.0035	-0.002	0.0025
	3	-0.0015	-0.001	-0.002	-0.0035	0.0025
	4	-0.001	0.000	-0.0022	-0.0055	0.0055
25	1	0.000	-0.002	-0.006	-0.006	0.006
	2	-0.0005	+0.001	-0.001	-0.003	0.004
	3	-0.00015	0.000	+0.001	0.000	0.0015
	4	-0.001	-0.003	-0.004	-0.003	0.003

(a) Traverses were 90 degrees apart along the length of the barrel.

(b) The value given is the difference between the maximum and minimum indicator readings along a given traverse.

TABLE B-4. STRAIGHTNESS MEASUREMENTS TAKEN ON AS-SWAGED UDINET 700 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (Inch) at Indicated Distance From End of Barrel				Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.	
31	1	0.000	+0.005	+0.005	+0.003	0.005
	2	+0.002	+0.003	+0.0015	0.000	0.003
	3	-0.0023	-0.0035	-0.0065	-0.006	0.0042
	4	+0.001	-0.001	-0.004	-0.004	0.005
32	1	0.000	-0.005	-0.007	-0.010	0.010
	2	-0.003	-0.0057	-0.0095	-0.009	0.0065
	3	-0.005	-0.001	-0.001	-0.0005	0.0045
	4	-0.002	0.000	+0.0015	0.000	0.002
33	1	0.000	+0.001	+0.001	+0.0004	0.001
	2	0.000	-0.001	-0.004	-0.003	0.004
	3	-0.001	-0.0028	-0.005	-0.0055	0.0045
	4	-0.001	0.000	0.000	-0.002	0.002
34	1	0.000	0.005	-0.001	-0.001	0.001
	2	+0.0035	.0017	0.000	-0.0015	0.005
	3	+0.004	-0.0043	+0.003	+0.0007	0.0036
	4	+0.001	+0.0025	+0.002	+0.001	0.0015
35	1	0.000	0.000	-0.001	-0.003	0.003
	2	+0.001	+0.0005	-0.002	-0.003	0.004
	3	0.000	-0.001	-0.003	-0.001	0.003
	4	-0.0005	-0.0012	-0.001	-0.001	0.0007
37	1	0.000	+0.002	+0.004	+0.004	0.004
	2	-0.0015	+0.001	+0.001	+0.0005	0.0025
	3	-0.0007	-0.003	-0.0075	-0.008	0.0073
	4	+0.0015	-0.002	-0.005	-0.0045	0.0063

TABLE B-4. STRAIGHTNESS MEASUREMENTS TAKEN ON AS-SWAGED UDINET 700 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (Inch) at Indicated Distance From End of Barrel				Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.	
31	1	0.000	+0.005	+0.005	+0.003	0.005
	2	+0.002	+0.003	+0.0015	0.000	0.003
	3	-0.0023	-0.0035	-0.0065	-0.006	0.0042
	4	+0.001	-0.001	-0.004	-0.004	0.005
32	1	0.000	-0.005	-0.007	-0.010	0.010
	2	-0.003	-0.0057	-0.0095	-0.009	0.0065
	3	-0.005	-0.001	-0.001	-0.0005	0.0045
	4	-0.002	0.000	+0.0015	0.000	0.002
33	1	0.000	+0.001	+0.001	+0.0004	0.001
	2	0.000	-0.001	-0.004	-0.003	0.004
	3	-0.001	-0.0028	-0.005	-0.0055	0.0045
	4	-0.001	0.000	0.000	-0.002	0.002
34	1	0.000	0.005	-0.001	-0.001	0.001
	2	+0.0035	.0017	0.000	-0.0015	0.005
	3	+0.004	-0.0043	+0.003	+0.0007	0.0036
	4	+0.001	+0.0025	+0.002	+0.001	0.0015
35	1	0.000	0.000	-0.001	-0.003	0.003
	2	+0.001	+0.0005	-0.002	-0.003	0.004
	3	0.000	-0.001	-0.003	-0.001	0.003
	4	-0.0005	-0.0012	-0.001	-0.001	0.0007
37	1	0.000	+0.002	+0.004	+0.004	0.004
	2	-0.0015	+0.001	+0.001	+0.0005	0.0025
	3	-0.0007	-0.003	-0.0075	-0.008	0.0073
	4	+0.0015	-0.002	-0.005	-0.0045	0.0065

TABLE B-4. (Continued)

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (inch) at Indicated Distance From End of Barrel			Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.
38	1	0.000	0.000	-0.0025	-0.003
	2	+0.0015	+0.001	-0.0004	-0.0005
	3	+0.002	+0.0015	+0.001	0.000
	4	0.000	0.000	-0.0015	-0.003

(a) Traverses were 90 degrees apart along the length of the barrel.

(b) The value given is the difference between the maximum and minimum indicator readings along a given traverse.

TABLE B-5. STRAIGHTNESS MEASUREMENTS TAKEN ON AS SWAGED CRUCIBLE ALLOY CG-27 GUN BARRELS

Gun Barrel Number	Traverse Number (a)	Dial Indicator Reading (inch) at Indicated Distance From End of Barrel			Total Indicator Reading (b) (T.I.R.), in.
		1-1/2 in.	8-1/2 in.	15-3/8 in.	22-3/8 in.
41	1	0.000	0.000	0.000	+0.0015
	2	-0.003	-0.0035	-0.005	-0.0065
	3	-0.0025	-0.003	-0.006	-0.0065
	4	0.000	0.000	-0.001	-0.001
42	1	0.000	+0.001	0.000	-0.002
	2	+0.004	+0.007	+0.005	+0.005
	3	+0.0035	+0.003	+0.0025	+0.004
	4	0.000	-0.003	-0.003	+0.002
43	1	0.000	-0.005	-0.0045	0.000
	2	-0.003	-0.001	0.000	-0.0004
	3	+0.002	+0.007	+0.004	-0.0002
	4	+0.0045	+0.003	-0.001	+0.0003
44	1	0.000	0.000	0.000	-0.001
	2	-0.0035	-0.008	-0.012	-0.012
	3	-0.005	-0.008	-0.010	-0.011
	4	-0.001	+0.0005	+0.002	0.000
45	1	0.000	+0.002	+0.0005	-0.0015
	2	+0.001	+0.0015	0.000	-0.0035
	3	-0.003	-0.006	-0.007	-0.0046
	4	-0.005	-0.005	-0.005	-0.003

(a) Traverses were 90 degrees apart along the length of the barrel.

(b) The value given is the difference between the maximum and minimum indicator readings along a given traverse.