

REPORT DOCUMENTATION PAGE			Form Approved OMB NO. 0704-0188		
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA, 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p>					
1. REPORT DATE (DD-MM-YYYY)		2. REPORT TYPE		3. DATES COVERED (From - To)	
		New Reprint		-	
4. TITLE AND SUBTITLE			5a. CONTRACT NUMBER		
Are Zr6-based MOFs water stable? Linkerhydrolysis vs. capillary-force-driven channel collapse			W911NF-13-1-0229		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER		
6. AUTHORS			5d. PROJECT NUMBER		
Joseph E. Mondloch, ^a Michael J. Katz, ^a Nora Planas, ^b David Semrouni, ^b Laura Gagliardi, ^b Joseph T. Hupp ^{*a} and Omar K. Farha ^{*ac}					
			5e. TASK NUMBER		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAMES AND ADDRESSES			8. PERFORMING ORGANIZATION REPORT NUMBER		
Northwestern University Evanston Campus Office for Sponsored Research (OSR) 1801 Maple Ave. Evanston, IL 60201 -3149					
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS (ES)			10. SPONSOR/MONITOR'S ACRONYM(S) ARO		
U.S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709-2211			11. SPONSOR/MONITOR'S REPORT NUMBER(S) 64434-CH.1		
12. DISTRIBUTION AVAILABILITY STATEMENT					
Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES					
The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.					
14. ABSTRACT					
Metal-organic frameworks (MOFs) built up from Zr6-based nodes and multi-topic carboxylate linkers have attracted attention due to their favourable thermal and chemical stability. However, the hydrolytic stability of some of these Zr6-based MOFs has recently been questioned. Herein we demonstrate that two Zr6-based frameworks, namely UiO-67 and NU-1000, are stable towards linker hydrolysis in					
15. SUBJECT TERMS					
Metal-organic frameworks (MOFs)					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	15. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE	UU		Omar Farha
UU	UU	UU			19b. TELEPHONE NUMBER
					847-467-4934

Report Title

Are Zr6-based MOFs water stable? Linkerhydrolysis vs. capillary-force-driven channel collapse

ABSTRACT

Metal–organic frameworks (MOFs) built up from Zr6-based nodes and multi-topic carboxylate linkers have attracted attention due to their favourable thermal and chemical stability. However, the hydrolytic stability of some of these Zr6-based MOFs has recently been questioned. Herein we demonstrate that two Zr6-based frameworks, namely UiO-67 and NU-1000, are stable towards linker hydrolysis in H₂O, but collapse during activation from H₂O. Importantly, this framework collapse can be overcome by utilizing solvent-exchange to solvents exhibiting lower capillary forces such as acetone.

REPORT DOCUMENTATION PAGE (SF298)
(Continuation Sheet)

Continuation for Block 13

ARO Report Number 64434.1-CH

Are Zr6-based MOFs water stable? Linkerhydro...

Block 13: Supplementary Note

© 2014 . Published in Chem. Commun., Vol. Ed. 0 50, (1) (2014), (, (1). DoD Components reserve a royalty-free, nonexclusive and irrevocable right to reproduce, publish, or otherwise use the work for Federal purposes, and to authorize others to do so (DODGARS §32.36). The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.

Approved for public release; distribution is unlimited.

Are Zr₆-based MOFs water stable? Linker hydrolysis vs. capillary-force-driven channel collapse†

Cite this: *Chem. Commun.*, 2014, 50, 8944Received 1st April 2014,
Accepted 20th June 2014

DOI: 10.1039/c4cc02401j


www.rsc.org/chemcomm

Joseph E. Mondloch,^a Michael J. Katz,^a Nora Planas,^b David Semrouni,^b Laura Gagliardi,^b Joseph T. Hupp*^a and Omar K. Farha*^{ac}

Metal–organic frameworks (MOFs) built up from Zr₆-based nodes and multi-topic carboxylate linkers have attracted attention due to their favourable thermal and chemical stability. However, the hydrolytic stability of some of these Zr₆-based MOFs has recently been questioned. Herein we demonstrate that two Zr₆-based frameworks, namely UiO-67 and NU-1000, are stable towards linker hydrolysis in H₂O, but collapse during activation from H₂O. Importantly, this framework collapse can be overcome by utilizing solvent-exchange to solvents exhibiting lower capillary forces such as acetone.

Metal–organic frameworks (MOFs) are a rapidly growing class of porous solid-state materials built up from inorganic nodes and organic linkers.¹ An important and emerging area of interest has been assessing the stability of MOFs. Surprisingly, of the approximately 20 000 known MOFs,² only a few dozen exhibit both the thermal and chemical stability desired for certain applications (such as catalysis in harsh environments).³ Examples of unusually stable MOFs include various zeolitic imidazolate frameworks (ZIFs),⁴ MILs,⁵ pyrazolate containing frameworks,⁶ and MOFs constructed from Zr₆-based nodes and carboxylate-terminated linkers.³ The prototypical example is UiO-66, a MOF built up from Zr₆(O)₄(OH)₄ nodes and benzene dicarboxylate linkers; UiO-66 is thermally (up to 500 °C),³ mechanically,⁷ hydrolytically, and chemically stable in a variety of organic solvents as well as acidic and basic aqueous media.^{3,8} The stability of Zr₆-based MOFs is attributed to the highly oxophilic nature of the Zr^{IV} sites and their Coulombic interaction with negatively charged termini of linkers.

Despite this, the hydrolytic stability of some Zr₆-based MOFs has recently come in to question. For example, it was reported

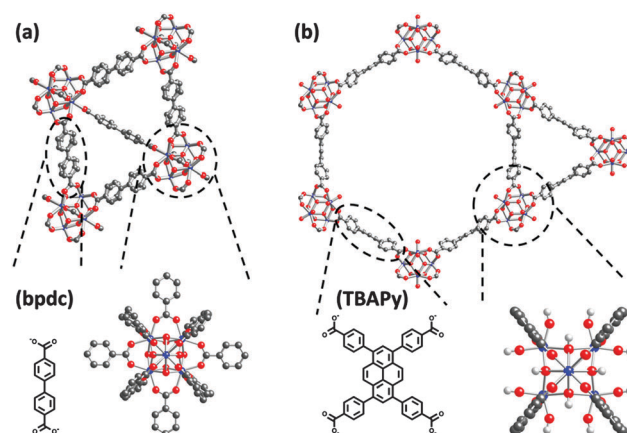

Scheme 1 Idealized molecular representations of (a) UiO-67 and (b) NU-1000.

that UiO-67 (Scheme 1)—a MOF isorecticular with UiO-66, but containing extended biphenyl dicarboxylate (bpdc) linkers—is not stable to H₂O exposure.^{8,9} This lack of stability was attributed to linker hydrolysis engendered by clustering of H₂O molecules near the Zr₆-based node (a phenomenon observed for other carboxylate containing MOFs¹⁰) and rotational effects of the extended linker.⁸ In contrast to these observations, others have found excellent hydrolytic stability in Zr₆-based MOFs with linkers of similar length to bpdc and even in MOFs with larger linkers and hence pores.¹¹

In the context of our labs' recent efforts utilizing Zr₆-based MOFs,¹² as well as our continuing efforts to elucidate the effects of activation on the stability and porosity of MOFs,¹³ we hypothesized that failures at the activation stage, as opposed to inherent hydrolytic Zr–carboxylate bond stability, could be the cause of the reported degradation of various Zr₆-based MOFs. Recall that activation entails removing guest molecules, such as solvent or other chemicals utilized during synthesis, from the MOF while maintaining its permanent porosity. We find that addressing issues related to activation can often yield permanently porous MOFs. Chief among these issues are destructive

^a Department of Chemistry, Northwestern University, 2145 Sheridan Road, Evanston, IL 60208, USA. E-mail: j-hupp@northwestern.edu, o-farha@northwestern.edu

^b Department of Chemistry, Supercomputing Institute & Chemical Theory Center, University of Minnesota, Minneapolis, MN 55455, USA

^c Department of Chemistry, Faculty of Science, King Abdulaziz University, Jeddah, Saudi Arabia

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c4cc02401j

(i.e., channel-collapsing) capillary forces which are greatest when solvent surface tension is high and when solvent molecules adhere well to MOF cavities or channels (e.g., *via* strong hydrogen bonding). Processes such as solvent-exchange,¹⁴ supercritical CO₂ (scCO₂) activation,¹⁵ and freeze-drying have all been employed to help avoid channel collapse in MOFs.¹⁶

Herein we demonstrate that two Zr₆-based MOFs, UiO-67 and NU-1000, are stable to linker hydrolysis under our experimental conditions. However, both frameworks are susceptible to capillary-force-driven channel collapse when activated directly from H₂O. Notably this can be overcome by simple solvent-exchange to acetone. Understanding the differences between linker hydrolysis and capillary-force-driven channel collapse will have a profound impact on the practical limitations of these Zr₆-based MOFs. For example, the former calls into question the viability of these frameworks for applications involving humid atmospheres, chemical catalysis, and electrocatalysis. In contrast, applications like dehumidification based cooling¹⁷ could indeed prove problematic if the H₂O-condensation limit is reached as capillary forces would then come into play during MOF regeneration.

UiO-67 was synthesized using the procedure recently reported by Katz *et al.*^{12b} The resultant powder X-ray diffraction (PXRD) pattern, Fig. 1a black line, nicely matches the simulated pattern of UiO-67 (gray line) confirming the bulk phase purity of the material. Next we placed UiO-67 in H₂O for 24 h and examined its PXRD pattern. As one might expect given the reported stability of the UiO series,³ the PXRD pattern is unaltered. However, upon heating the sample to 150 °C under vacuum and removing the H₂O molecules from the pores of UiO-67 (i.e., activating the sample), a noticeable broadening of the peaks at angles (2θ) of 5.8 and 6.7 degrees was observed along with nearly complete disappearance of the peaks at higher 2θ (Fig. 1a, red trace). We suspected this loss of crystallinity was due to capillary forces that in turn cause partial or complete framework collapse during activation. To circumvent this problem we exchanged the H₂O molecules to acetone and subsequently activated the sample thermally (Fig. 1a, blue line).

Pleasingly the crystallinity of UiO-67 was maintained after solvent-exchange to acetone. We also rigorously quantified the relative crystallinity for these UiO-67 samples (and NU-1000, *vide infra*) in the ESI.†

To further elucidate the effects of activating UiO-67 from both H₂O and acetone, N₂ adsorption isotherms of thermally activated UiO-67 (i.e., DMF synthesis solvent evacuated), a sample activated directly from H₂O, and a sample activated *via* solvent-exchange to acetone (Fig. 1c) were measured. Activation directly from H₂O (red triangles) leads to a complete loss of porosity. However, when solvent-exchange to acetone is utilized the porosity of UiO-67 is retained, Fig. 1c (comparison of black circles and blue squares).

Next we turned our attention to the MOF NU-1000 ([Zr₆(OH)₁₆(TBAPy)₂]) which is built up from Zr₆(OH)₁₆ containing nodes and 1,3,6,8-tetrakis(benzoate)pyrene (TBAPy) linkers (Scheme 1).^{12a} NU-1000 has triangular micropores as well as exceptionally large mesopores (ca. 30 Å diameter). In this regard, NU-1000 should facilitate the permeation of H₂O throughout its structure and ensure H₂O molecules can readily access its node. Using the procedure detailed by Mondloch *et al.*,^{12a} NU-1000 was synthesized as a microcrystalline powder. The PXRD pattern and N₂ adsorption isotherms are shown in Fig. 1b and d (black line and black circles). Examination of the PXRD patterns of NU-1000 soaked in H₂O for 24 h but not activated (Fig. 1b, green a line), activated directly from H₂O (Fig. 1b, red line), and solvent-exchanged to acetone followed by thermal activation (Fig. 1b, blue line) reveal that the crystallinity is maintained except when NU-1000 is activated directly from H₂O. In particular the reflections centered at 5 and 7.5 degrees have broadened, while the peaks at higher angles have decreased in intensity. Consistent with the UiO-67 sample, N₂ adsorption isotherms (Fig. 1d) demonstrate that the sample activated directly from H₂O (Fig. 1d, red triangles) exhibits significantly less porosity than either the pristine NU-1000 sample or the one activated *via* solvent-exchange (Fig. 1d, black circles and blue squares). For example, the BET surface area of the sample activated from H₂O is 480 m² g⁻¹, while pristine NU-1000 has a surface area of 2040 m² g⁻¹.

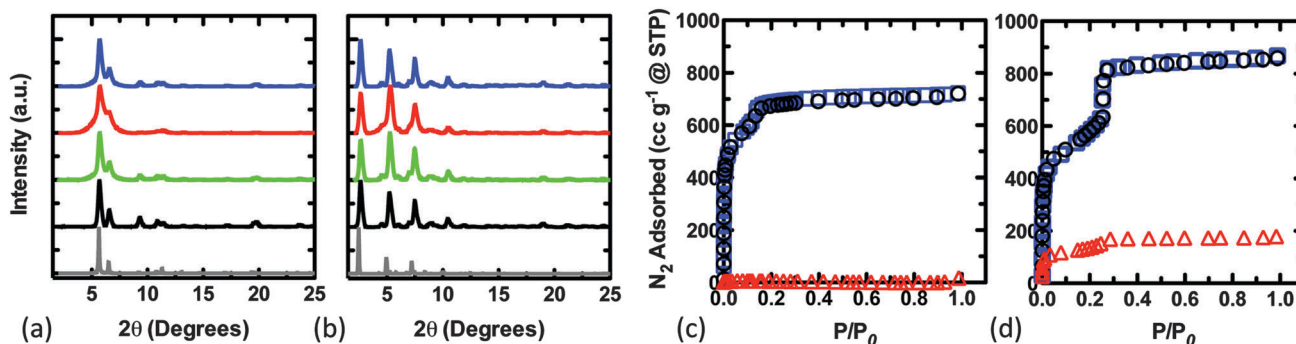


Fig. 1 Normalized PXRD patterns of the simulated structures (gray line), parent MOFs (black line), MOFs in H₂O (green line), MOFs thermally activated from H₂O (red line), and MOFs solvent-exchanged to acetone and subsequently activated (blue line) for UiO-67 (a) and NU-1000 (b). For UiO-67 (c) and NU-1000 (d): N₂ adsorption isotherms of samples activated *via* thermal evacuation of the synthesis solvent (DMF or acetone, black circles), thermal evacuation of H₂O from the pores (red triangles), and exchange of H₂O for acetone, and then thermal evacuation (blue squares). For clarity only every other data point is displayed in the isotherms.

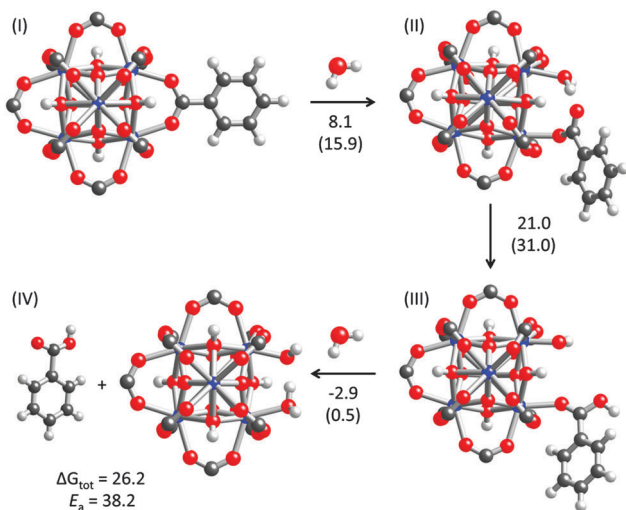


Fig. 2 Molecular representations and DFT free energies (in kcal mol⁻¹) associated with the hypothetical hydrolytic degradation of UiO-67. In parenthesis, the corresponding activation free energy.

We further ruled out the hydrolytic pathway in UiO-67 and NU-1000 through a combination of NMR and IR spectroscopies (ESI[†]) as well as quantum chemical characterization. ¹H NMR of the filtrate from the H₂O soaked samples showed no residual sign of their linkers in solution. Diffuse Reflectance Infrared Fourier Transform Spectroscopy (DRIFTS) demonstrated that both the UiO-67 and NU-1000 frameworks stayed intact after exposure to H₂O, solvent exchange to acetone, and finally thermally activating the samples. In contrast, DRIFTS of the samples activated directly from H₂O show broad stretches consistent with the presence of free carboxylates and loss of framework porosity (*i.e.*, node-linker bond breaking occurring during activation). Interestingly we also performed *in situ* DRIFTS experiments (ESI[†]). Exposure of UiO-67 and NU-1000 to H₂O vapour, followed by removal of excess H₂O yielded no detectable change in the DRIFTS spectra, a result suggesting that the stability of these frameworks towards H₂O vapor is different than for condensed phase H₂O. Finally, cluster model density functional theory, DFT, calculations (at the M06-L level, see ESI[†]) are consistent with the node of UiO-67 being stable towards hydrolytic attack. The computed free energies of the proposed degradation pathway are summarized in Fig. 2; the net free energy is approximately +26 kcal mol⁻¹ with an overall activation energy of 38 kcal mol⁻¹. This is in good agreement with recent calculations from Vermoortele *et al.* demonstrating that removal of CF₃COO⁻ anions from Zr₆ containing nodes is also thermodynamically uphill.¹⁸

Rather than hydrolytic instability through H₂O clustering, our data demonstrate instability arises from the presence of capillary forces experienced during activation. Notably, mild activation strategies—such as solvent-exchange (or scCO₂, no surface tension)—can be utilized to overcome framework collapse. While the surface tension of H₂O is significantly larger than that of acetone (72 mN m⁻¹ vs. 26 mN m⁻¹ at 25 °C),¹⁹ a discussion based on the geometrical properties of the pores of UiO-67 and NU-1000, as well as the literature on confined H₂O (ESI[†]), brings additional insight into the behaviour of H₂O molecules and capillary forces in Zr₆-based MOFs. Although additional data

would be required to quantify these effects, our initial exploration suggests that H₂O does not behave as a liquid in UiO-67, while it should partially behave as a liquid in the larger pores of NU-1000. This in turn implies that solvent-framework intermolecular forces are significant in driving channel collapse for Zr₆-based MOFs when activated from H₂O.

J.T.H., N.P., D.S., and L.G. gratefully acknowledge funding from the U.S. DOE, Office of Basic Energy Sciences, Division of Chemical Sciences, Geosciences and Biosciences (Award DE-FG02-12ER16362). J.E.M., M.J.K., and O.K.F. gratefully acknowledge funding from the Army Research Office (project number W911NF-13-1-0229).

Notes and references

- (a) O. M. Yaghi, M. O'Keefe, N. W. Ockwig, H. K. Chae, M. Eddaoudi and J. Kim, *Nature*, 2003, **423**, 705; (b) G. Férey, *Chem. Soc. Rev.*, 2008, **37**, 191; (c) S. Horike, S. Shimomura and S. Kitagawa, *Nat. Chem.*, 2009, **1**, 695.
- H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444.
- J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850.
- K. S. Park, Z. Ni, A. P. Côté, J. Y. Choi, R. Huang, F. J. Uribe-Romo, H. K. Chae, M. O'Keefe and O. M. Yaghi, *PNAS*, 2006, **103**, 10186.
- G. Férey, C. Mellot-Drazniéks, C. Serre, F. Millange, J. Dutour, S. Surblé and I. Margiolaki, *Science*, 2005, **309**, 2040.
- V. Colombo, S. Galli, H. J. Choi, G. D. Han, A. Maspero, G. Palmisano, N. Masciocchi and J. R. Long, *Chem. Sci.*, 2011, **2**, 1311.
- H. Wu, T. Yildirim and W. Zhou, *J. Phys. Chem. Lett.*, 2013, **4**, 925.
- J. B. Decoste, G. W. Peterson, H. Jasuja, T. G. Glover, Y.-G. Huang and K. S. Walton, *J. Mater. Chem. A*, 2013, **1**, 5642.
- G. C. Shearer, S. Forselv, S. Chavan, S. Bordiga, K. Mathisen, M. Bjørgen, S. Svelle and K. P. Lillerud, *Top. Catal.*, 2013, **56**, 770.
- P. Küsgens, M. Rose, I. Senkowska, H. Fröde, A. Henschel, S. Siegle and S. Kaskel, *Microporous Mesoporous Mater.*, 2009, **120**, 325.
- (a) W. Morris, B. Voloskiy, S. Demir, F. Gándara, P. L. McGrier, H. Furukawa, D. Cascio, J. F. Stoddart and O. M. Yaghi, *Inorg. Chem.*, 2012, **51**, 6443; (b) H.-L. Jiang, D. Feng, K. Wang, Z.-Y. Gu, Z. Wei, Y.-P. Chen and H.-C. J. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 13934; (c) D. Feng, W.-C. Chung, Z. Wei, Z.-Y. Gu, H.-L. Jiang, Y.-P. Chen, D. J. Darensbourg and H.-C. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 17105; (d) D. Feng, Z.-Y. Gu, J.-R. Li, H.-L. Jiang, Z. Wei and H.-C. Zhou, *Angew. Chem., Int. Ed.*, 2012, **51**, 10307; (e) M. Carboni, C. W. Abney, S. Liu and W. Lin, *Chem. Sci.*, 2013, **4**, 2396; (f) Y. Chen, T. Hoang and S. Ma, *Inorg. Chem.*, 2012, **51**, 12600.
- (a) J. E. Mondloch, W. Bury, D. Fairen-Jimenez, S. Kwon, E. J. DeMarco, M. H. Weston, A. A. Sarjeant, S. T. Nguyen, P. C. Stair, R. Q. Snurr, O. K. Farha and J. T. Hupp, *J. Am. Chem. Soc.*, 2013, **135**, 10294; (b) M. J. Katz, Z. J. Brown, Y. J. Colón, P. W. Siu, K. A. Scheidt, R. Q. Snurr, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2013, **49**, 9449; (c) M. J. Katz, J. E. Mondloch, R. K. Totten, J. K. Park, S. T. Nguyen, O. K. Farha and J. T. Hupp, *Angew. Chem., Int. Ed.*, 2013, **53**, 497.
- (a) O. K. Farha and J. T. Hupp, *Acc. Chem. Res.*, 2010, **43**, 1166; (b) J. E. Mondloch, O. Karagiari, O. K. Farha and J. T. Hupp, *CrystEngComm*, 2013, **15**, 9258; (c) O. K. Farha, A. Ö. Yazaydin, I. Eryazici, C. D. Malliakas, B. G. Hauser, M. G. Kanatzidis, S. T. Nguyen, R. Q. Snurr and J. T. Hupp, *Nat. Chem.*, 2010, **2**, 944; (d) O. K. Farha, I. Eryazici, N. C. Jeong, B. G. Hauser, C. E. Wilmer, A. A. Sarjeant, R. Q. Snurr, S. T. Nguyen, A. Ö. Yazaydin and J. T. Hupp, *J. Am. Chem. Soc.*, 2012, **134**, 15016.
- H. Li, M. Eddaoudi, M. O'Keefe and O. M. Yaghi, *Nature*, 1999, **402**, 276.
- A. P. Nelson, O. K. Farha, K. L. Mulfort and J. T. Hupp, *J. Am. Chem. Soc.*, 2009, **131**, 458.
- L. Ma, A. Jin, Z. Xie and W. Lin, *Angew. Chem., Int. Ed.*, 2009, **48**, 9905.
- H. Furukawa, F. Gándara, Y.-B. Zhang, J. Jiang, W. L. Queen, M. R. Hudson and O. M. Yaghi, *J. Am. Chem. Soc.*, 2014, **136**, 4369.
- F. Vermoortele, B. Bueken, G. Le Bars, B. Van de Voorde, M. Vandichel, K. Houthoofd, A. Vimont, M. Daturi, M. Waroquier, V. Van Speybroeck, C. Kirschhock and D. E. De Vos, *J. Am. Chem. Soc.*, 2013, **135**, 11465.
- Handbook of Chemistry and Physics*, Chemical Rubber Publishing Company, Boca Taton, FL, 2003.