



ARL-MR-0930 • MAY 2016



Ballistic Evaluation of 2060 Aluminum

by Denver B Gallardy

Approved for public release; distribution is unlimited.

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.



Ballistic Evaluation of 2060 Aluminum

by Denver B Gallardy

Weapons and Materials Research Directorate, ARL

REPORT DOCUMENTATION PAGE				<i>Form Approved</i> <i>OMB No. 0704-0188</i>	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) May 2016		2. REPORT TYPE Memorandum Report		3. DATES COVERED (From - To) 1 January 2013–31 October 2014	
4. TITLE AND SUBTITLE Ballistic Evaluation of 2060 Aluminum				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Denver B Gallardy				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) US Army Research Laboratory ATTN: RDRL-WMP-E Aberdeen Proving Ground, MD 21005-5066				8. PERFORMING ORGANIZATION REPORT NUMBER ARL-MR-0930	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT The US Army Research Laboratory evaluated the ballistic performance of aluminum alloy (AA) 2060-T8 produced by Alcoa as part of a Defense Acquisition Challenge Program. Ballistic evaluation was performed using armor-piercing and fragment-simulating projectiles to determine the V₅₀ ballistic-protection limit (V₅₀) for various thicknesses of material. The V₅₀ was then compared with other ballistic-grade AAs, namely AA2195 and AA2139. The results of these experiments were used to derive the acceptance tables for AA2060 included in the updated military specification MIL-DTL-32341A (MR).					
15. SUBJECT TERMS aluminum, armor, V₅₀, 2060, 6055, Defense Acquisition Challenge, ballistic acceptance					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UU	18. NUMBER OF PAGES 66	19a. NAME OF RESPONSIBLE PERSON Denver B Gallardy
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code) 410-278-6510

Contents

List of Figures	iv
List of Tables	iv
Acknowledgments	v
1. Introduction	1
2. Experimental Procedure	2
3. Test Projectiles	3
3.1 Armor-Piercing Projectiles	3
3.2 Fragment-Simulating Projectiles	4
4. Results and Analysis	5
5. Conclusions	10
6. References	11
Appendix A. Ballistic Test Data: Individual Shot Results	13
Appendix B. Additional Ballistic Test Data	51
List of Symbols, Abbreviations, and Acronyms	55
Distribution List	56

List of Figures

Fig. 1	Typical test setup	3
Fig. 2	AP projectiles.....	4
Fig. 3	FSP projectiles	4
Fig. 4	Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.30-cal. APM2 at 30° obliquity.....	7
Fig. 5	Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.30-cal. APM2 at 0° obliquity	7
Fig. 6	Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.50-cal. APM2 at 0° obliquity	8
Fig. 7	Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.50-cal. FSP at 0° obliquity	8
Fig. 8	Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 20-mm FSP at 0° obliquity	9

List of Tables

Table 1	Test matrix for AA2060 indicating the number of plates tested.....	1
Table 2	Chemistry of AAs' weight-percent ranges	2
Table 3	AP projectiles' physical characteristics	4
Table 4	APM2 0.30-cal., 30° obliquity V_{50} ballistic limits for AA2060	5
Table 5	APM2 0.30-cal., 0° obliquity V_{50} ballistic limits for AA2060	5
Table 6	APM2 0.50-cal., 0° obliquity V_{50} ballistic limits for AA2060	5
Table 7	FSP 0.50-cal., 0° obliquity V_{50} ballistic limits for AA2060	6
Table 8	FSP 20-mm, 0° obliquity V_{50} ballistic limits for AA2060	6
Table 9	Constants of regression for the acceptance curves for AA2060	10
Table B-1	APM2 0.30-cal., 30° obliquity ballistic performance	52
Table B-2	APM2 0.30-cal., 0° obliquity ballistic performance	52
Table B-3	APM2 0.50-cal., 0° obliquity ballistic performance	52
Table B-4	0.50-cal. FSP, 0° obliquity ballistic performance	52
Table B-5	FSP 20-mm, 0° obliquity ballistic performance	53

Acknowledgments

The author would like to thank Alcoa, and specifically Phil Smith and Rick Kane, for producing and providing, in-kind, the armor-plate test articles. The author also thanks Donald Little of the US Army Research Laboratory's Armor Mechanisms Branch (ARL/MB), Phil Davis of Dynamic Science, Inc., and David Churn of Bowhead Science and Technology, LLC, for performing the ballistic experiments in Experimental Facilities (EFs) 108 and 106, as well as John Hogan of ARL/AMB, Hugh Walter of Bowhead Science and Technology, and David Handshoe and William Bryant of Dynamic Science for performing the ballistic experiments in EF-110.

The author also acknowledges the outstanding contributions of the following people who made this work possible: program lead Brian Placzankis of ARL's Coatings, Corrosion and Engineered Polymers Branch and William "Randy" Everett and Rino Imperiale of the Army Research, Development and Engineering Command's Comparative Technology Office. The author also thanks Robert "Gun Bob" Thompson from the Office of Secretary of Defense's Comparative Technology Office, Office of the Deputy Assistant Secretary of Defense for Emerging Capability and Prototyping.

INTENTIONALLY LEFT BLANK.

1. Introduction

In 2012 a Defense Acquisition Challenge (DAC) program proposal was submitted to the US Office of the Secretary of Defense (OSD) to provide improved armor-plate materials for production and repair of existing or new aluminum (Al)-based monocoque armored-vehicle hulls such as those of the M2 Bradley Infantry Fighting Vehicles. Also in 2012 the Aluminum Association assigned a new 2XXX-series alloy designation to Alcoa for aluminum alloy (AA) 2060, granting it full commercial availability as rolled plate from Davenport, IA. AA2060 remains under patent protection and is solely manufactured by Alcoa. AA2060 was confirmed as having similar mechanical properties as the AA2195 alloy and therefore became the basis for a fiscal year 2012 OSD-funded DAC program to fully validate and ultimately transition AA2060 for availability as an appliqué armor plate in US acquisition. The ballistics goal of this program was to verify that AA2060-T8 met or exceeded the performance of AA2195-T64.¹

Several thicknesses of 2060-T8 were provided to ARL by Alcoa. Table 1 is a summary matrix of the tested thicknesses subjected to impacts from various munitions including armor-piercing (AP) and fragment-simulating projectiles (FSPs). Additionally, Table 2 provides the required chemistries for AA2060 as well as other common Al-armor alloys.

Table 1 Test matrix for AA2060 indicating the number of plates tested

Nominal plate gage (mm)	0.30-cal. APM2 30° obliquity	0.30-cal. APM2 0° obliquity	0.50-cal. APM2 0° obliquity	0.50-cal. FSP 0° obliquity	20-mm FSP 0° obliquity
12.70	2	...	...	...	...
19.05	1	1	...	1	...
25.40	...	3	...	3	3
31.75	...	1	...	...	1
38.10	...	4	4	...	4
50.80	...	...	3	...	2
57.15	...	...	1	...	...
63.50	...	...	2	...	...

Table 2 Chemistry of AAs' weight-percent ranges²

Element	2139	2195	2519	5083	6061	2060	7039	7085
Copper	4.5–5.5	3.70–4.30	5.30–6.40	0.10 max	0.15–0.40	3.40–4.50	0.10 max	1.3–2.0
Iron	0.15 max	0.15 max	0.30 max ^a	0.40 max	0.70 max	0.07 max	0.40 max	0.08 max
Lithium	...	0.80–1.20	...	...	...	0.60–0.90	...	...
Chromium	0.05 max	...	...	0.05–0.25	0.04–0.35	...	0.15–0.25	0.04 max
Manganese	0.20–0.60	0.25 max	0.10–0.50	0.40–1.0	0.15 max	0.10–0.50	0.10–0.40	0.04 max
Magnesium	0.20–0.80	0.25–0.80	0.05–0.40	4.0–4.90	0.8–1.2	0.60–1.10	2.30–3.30	1.2–1.8
Silicon	0.10 max	0.12 max	0.25 max ^a	0.40 max	0.40–0.80	0.07 max	0.30 max	0.06 max
Titanium	0.15 max	0.10 max	0.02–0.10	0.15 max	0.15 max	0.10 max	0.10 max	0.06 max
Zinc	0.25 max	0.25 max	0.10 max	0.25 max	0.25 max	0.30–0.50	3.50–4.50	7.0–8.0
Zirconium	...	0.08–0.16	0.10–0.25	...	...	0.05–0.15	...	0.08–0.15
Silver	0.15–0.60	0.25–0.60	...	...	...	0.05–0.50	...	...
Others (each)	0.05 max	0.05 max	0.05 max	0.05 max	0.05 max	0.05 max	0.05 max	0.05 max
Others (total)	0.15 max	0.15 max	0.15 max	0.15 max	0.15 max	0.15 max	0.15 max	0.15 max
Aluminum	Remainder	Remainder	Remainder	Remainder	Remainder	Remainder	Remainder	Remainder

^aThe total weight percentage of the combination of silicon and iron cannot exceed 0.40%.

2. Experimental Procedure

The V_{50} is defined as the impact velocity at which the projectile is equally as likely to penetrate the target as it is to arrest. A 0.51-mm (0.020-inch) 2024 T3 Al witness plate was positioned 152 mm (6 inches) behind the target to determine the outcome of each shot. An impact is regarded as a complete penetration (CP), or loss, if the projectile or a resulting target fragment from impact creates a hole in the witness plate through which light can be observed. If an impact does not result in a CP, it is considered a partial penetration (PP), or win. To keep results as consistent as possible, only shots conforming to the following conditions were used to determine the V_{50} : The projectile must be unyawed—less than 2° of total yaw for AP rounds and less than 5° of total yaw for FSPs—and strike the target at least 2 projectile diameters from any previous impact or damage or the edge of the target. Total yaw is defined as the vector sum of the projectile's pitch and yaw. The V_{50} is calculated by the arithmetic mean of an equal number of CPs and PPs within an 18-m/s (60-ft/s) spread for a 2 + 2 V_{50} , a 27-m/s (90-ft/s) spread for a 3 + 3 V_{50} , and as small of a spread as attainable for a 5 + 5 V_{50} .³

Projectile velocities for the determination of the V_{50} were measured using one of 2 methods, as shown in Fig. 1. The first method is an orthogonal flash X-ray system, described in detail by Grabarek and Herr,⁴ which also measures pitch and yaw. The second method uses 3 infrared (IR) screens and a chronograph. The velocity is calculated using the first and third screens with the middle screen used to check for

bad readings. The flash X-ray method was used in situations with projectiles that historically exhibit excessive yaw or if space did not allow for the use of the IR break screens. When the IR break screens and chronograph were used, the projectile velocity was corrected to the target-impact location using a correction factor based on an initial flash X-ray reading at the impact location. The correction was made using Eqs. 1 and 2 in lieu of using the following air-drag factors:

$$\frac{(\text{x-ray velocity})}{(\text{chronograph velocity})} = (\text{correction factor}). \quad (1)$$

$$(\text{correction factor}) \times (\text{chronograph velocity}) = (\text{corrected velocity}). \quad (2)$$

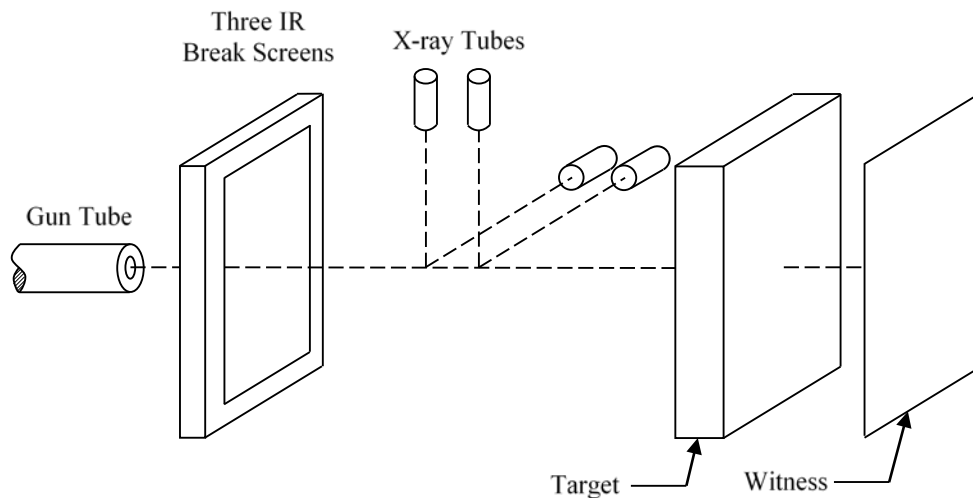


Fig. 1 Typical test setup

3. Test Projectiles

3.1 Armor-Piercing Projectiles

The US 0.30-cal. and 0.50-cal. APM2 are the 2 AP projectiles that were used in this study. These projectiles are shown in Fig. 2. The APM2 projectiles have hardened steel cores with a Rockwell hardness of C61–65. The physical characteristics of these projectiles are listed in Table 3.

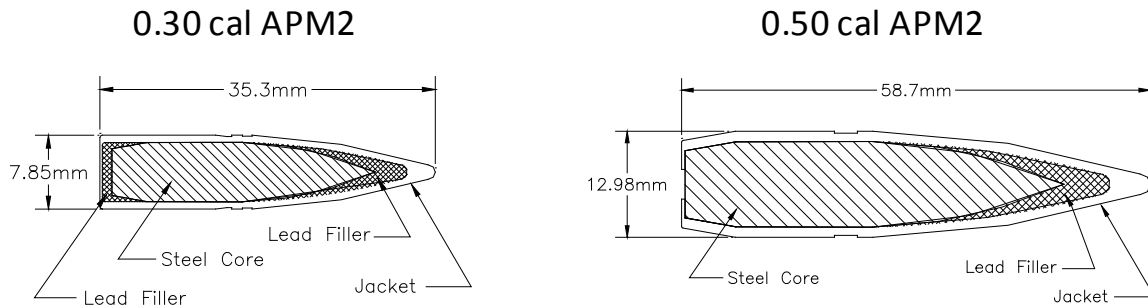


Fig. 2 AP projectiles

Table 3 AP projectiles' physical characteristics⁵

Projectile type	Projectile			Core		
	Length (mm)	Diameter (mm)	Weight (g)	Length (mm)	Diameter (mm)	Weight (g)
0.30-cal. APM2	35.3	7.85	10.8	27.4	6.2	5.3
0.50-cal. APM2	58.7	12.98	45.9	47.5	10.9	25.9

3.2 Fragment-Simulating Projectiles

FSPs (Fig. 3) are a family of projectiles that are flat-nosed right circular cylinders manufactured to MIL-DTL-46593B (MR).⁶ These projectiles are used in material evaluations and acceptance testing to simulate performance against fragments produced from improvised explosive devices and artillery. Both 0.50-cal. and 20-mm FSPs were used for the evaluation of AA2060.

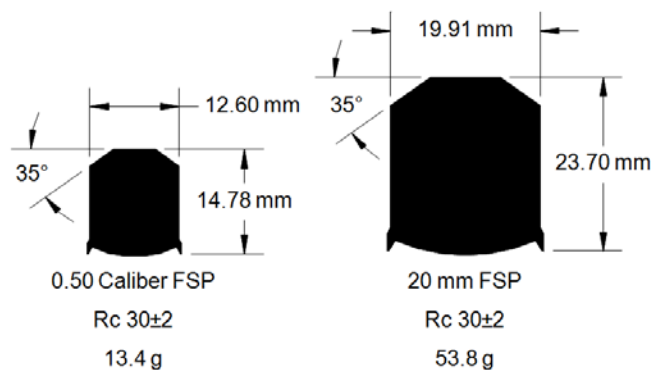


Fig. 3 FSP projectiles

4. Results and Analysis

The test results are summarized in Tables 4–8. The individual shot records are provided in Appendix A, and ballistic data obtained by the US Army Aberdeen Test Center (ATC)⁷ are included in Appendix B.

Table 4 APM2 0.30-cal., 30° obliquity V₅₀ ballistic limits for AA2060

Plate ID	Nominal thickness		Actual thickness		Areal density		V ₅₀		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(lb/ft ²)	(m/s)	(ft/s)	(m/s)	(ft/s)
215-014	12.70	0.50	15.98	0.629	43.33	8.88	586	1,921	6	19
215-016	12.70	0.50	17.22	0.678	46.71	9.57	628	2,059	6	19
425-801	19.05	0.75	21.62	0.851	58.63	12.01	707	2,319	4	14

Table 5 APM2 0.30-cal., 0° obliquity V₅₀ ballistic limits for AA2060

Plate ID	Nominal thickness		Actual thickness		Areal density		V ₅₀		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(lb/ft ²)	(m/s)	(ft/s)	(m/s)	(ft/s)
425-801	19.05	0.75	21.62	0.851	58.63	12.01	642	2,107	7	22
215-019	25.40	1.00	22.89	0.901	62.07	12.71	659	2,161	9	30
425-871	25.40	1.00	22.81	0.898	61.86	12.67	667	2,189	8	26
425-841	25.40	1.00	24.38	0.960	66.14	13.55	684	2,243	9	29
425-811	31.75	1.25	30.18	1.188	81.84	16.76	779	2,556	11	36
425-822	38.10	1.50	36.93	1.454	100.17	20.52	889	2,916	6	19
425-852	38.10	1.50	36.60	1.441	99.27	20.33	879	2,884	9	28
215-012	38.10	1.50	38.10	1.500	103.34	21.17	898	2,945	8	26
215-006	38.10	1.50	38.56	1.518	104.58	21.42	906	2,972	7	24

Table 6 APM2 0.50-cal., 0° obliquity V₅₀ ballistic limits for AA2060

Plate ID	Nominal thickness		Actual thickness		Areal density		V ₅₀		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(lb/ft ²)	(m/s)	(ft/s)	(m/s)	(ft/s)
425-822	38.10	1.50	36.93	1.454	100.17	20.52	650	2,132	10	32
425-852	38.10	1.50	36.60	1.441	99.27	20.33	648	2,127	5	17
215-012	38.10	1.50	38.10	1.500	103.34	21.17	652	2,140	5	18
215-006	38.10	1.50	38.56	1.518	104.58	21.42	660	2,164	9	28
425-821	50.80	2.00	49.66	1.955	134.68	27.59	772	2,532	6	21
425-851	50.80	2.00	49.50	1.949	134.27	27.50	765	2,509	7	24
425-881	50.80	2.00	49.68	1.956	134.75	27.60	767	2,517	10	32
215-011	57.15	2.25	54.99	2.165	149.15	30.55	806	2,646	6	19
425-831	63.50	2.50	62.08	2.444	168.37	34.48	873	2,864	4	13
425-861	63.50	2.50	61.75	2.431	167.47	34.30	868	2,847	11	36

Table 7 FSP 0.50-cal., 0° obliquity V₅₀ ballistic limits for AA2060

Plate ID	Nominal thickness		Actual thickness		Areal density		V ₅₀		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(lb/ft ²)	(m/s)	(ft/s)	(m/s)	(ft/s)
425-801	19.05	0.75	21.62	0.851	58.63	12.01	766	2,514	7	23
215-019	25.40	1.00	22.89	0.901	62.07	12.71	914	2,998	6	19
425-871	25.40	1.00	22.81	0.898	61.86	12.67	903	2,962	6	21
425-841	25.40	1.00	24.38	0.960	66.14	13.55	987	3,239	11	35

Table 8 FSP 20-mm, 0° obliquity V₅₀ ballistic limits for AA2060

Plate ID	Nominal thickness		Actual thickness		Areal density		V ₅₀		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(lb/ft ²)	(m/s)	(ft/s)	(m/s)	(ft/s)
215-019	25.40	1.00	22.94	0.903	62.21	12.74	427	1,401	17	56
425-871	25.40	1.00	22.96	0.904	62.28	12.76	396	1,298	5	16
425-841	25.40	1.00	24.21	0.953	65.65	13.45	447	1,468	5	17
425-811	31.75	1.25	30.05	1.183	81.50	16.69	599	1,965	6	19
425-822	38.10	1.50	37.03	1.458	100.44	20.57	881	2,892	8	25
425-852	38.10	1.50	36.60	1.441	99.27	20.33	865	2,839	5	17
215-012	38.10	1.50	38.10	1.500	103.34	21.17	909	2,983	7	22
215-006	38.10	1.50	38.43	1.513	104.23	21.35	923	3,027	1	3
425-821	50.80	2.00	49.53	1.950	134.34	27.51	1213	3,979	6	21
425-851	50.80	2.00	49.53	1.950	134.34	27.51	1233	4,047	8	25

The results of the ballistic evaluation are compared directly against the acceptance curves of AA2195 and AA2139 in MIL-DTL-32341A.¹ Figures 4–8 show the AA2060 test data collected by ARL and ATC as compared with the other specification. The data displayed are the V₅₀ as a function of the plate thickness. To allow for a fair comparison against the existing specification, a line depicting the V₅₀ –2σ was plotted against the acceptance spec. This line represents a V₀₂ rather than a V₅₀. To ensure successful protection at a given thickness, the lower band of the 2σ distribution (V₀₂ line) is used to define minimum acceptable performance. A V₅₀ falling below this line is considered unacceptable. For comparison purposes it should also be noted that the plates are compared on a thickness basis to be consistent with the specifications; however, the densities of the alloys vary slightly. Both AA2060 and AA2195 have a density of 2.71 g/cm³ whereas AA2139 has a density of 2.80 g/cm³.

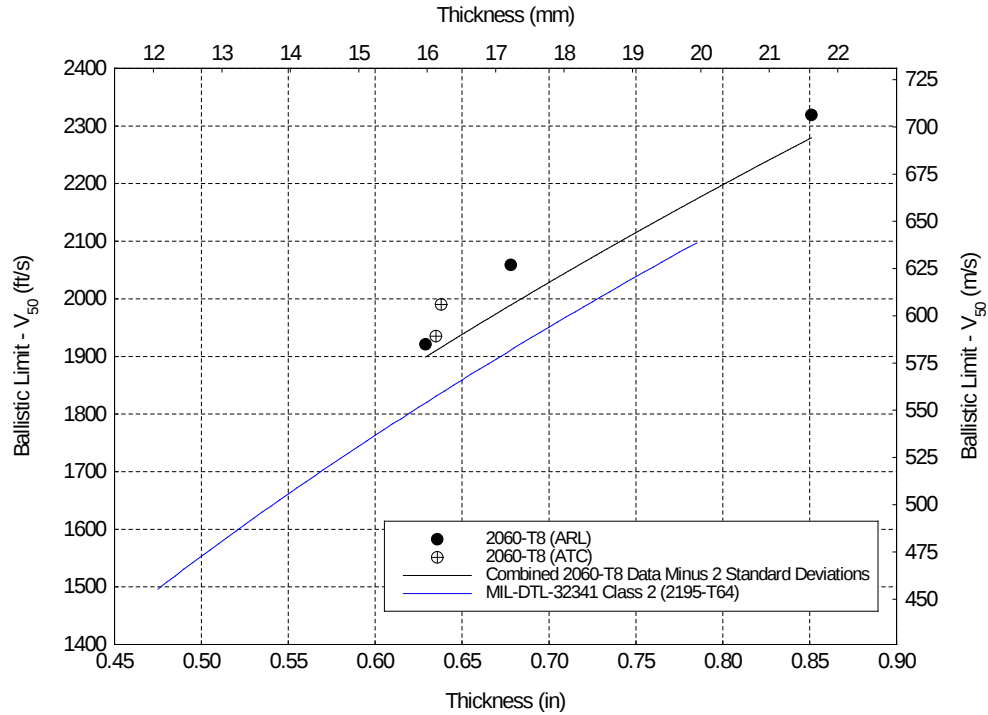


Fig. 4 Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.30-cal. APM2 at 30° obliquity

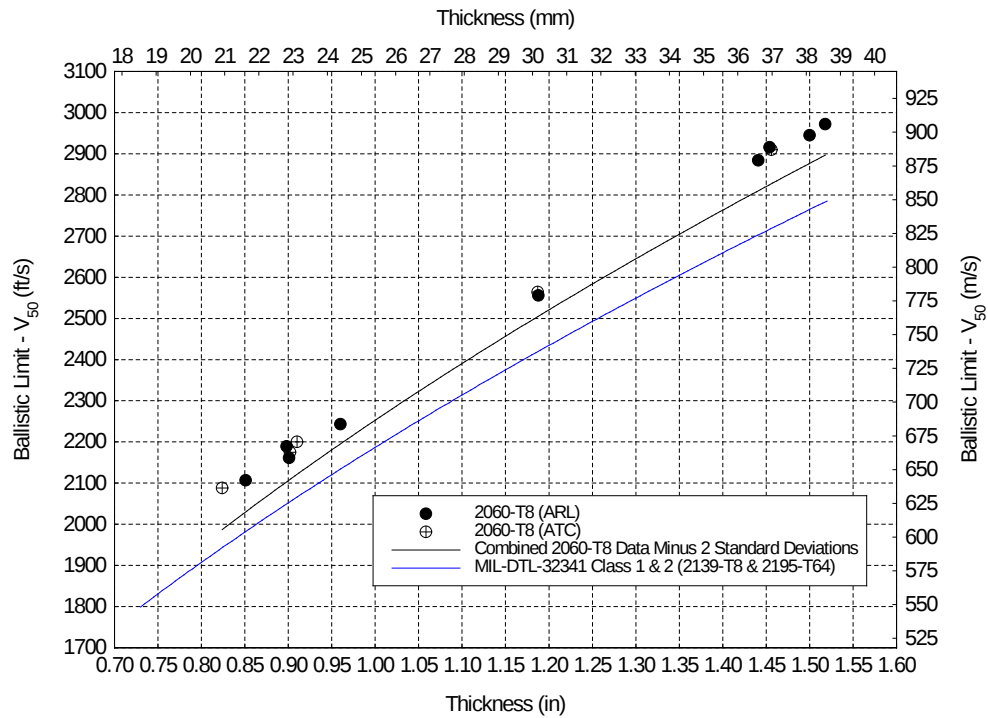


Fig. 5 Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.30-cal. APM2 at 0° obliquity

Approved for public release; distribution is unlimited.

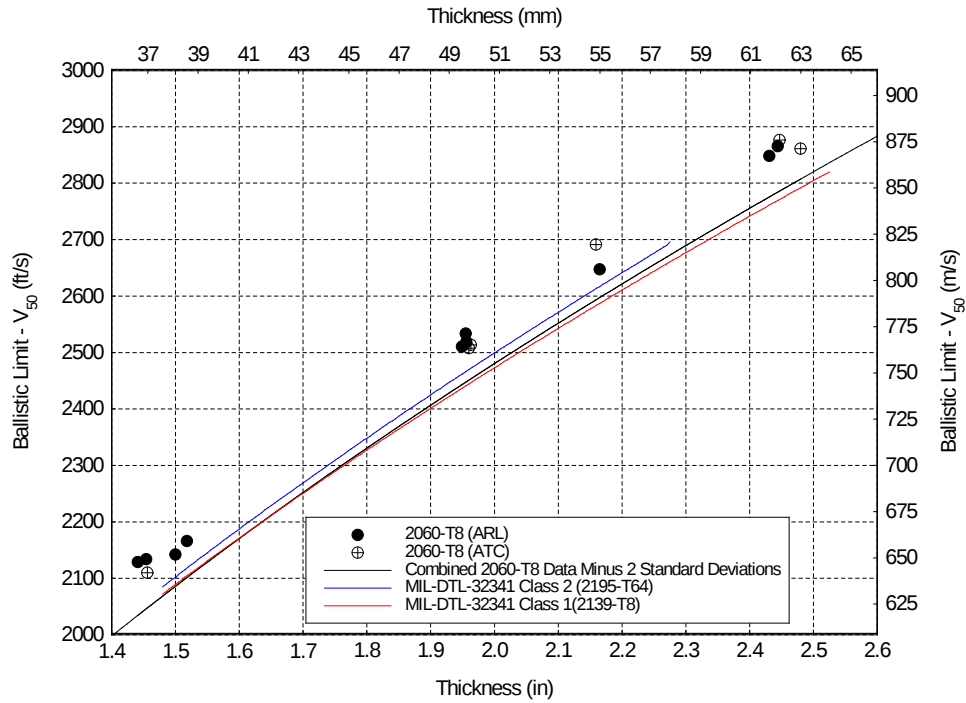


Fig. 6 Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.50-cal. APM2 at 0° obliquity

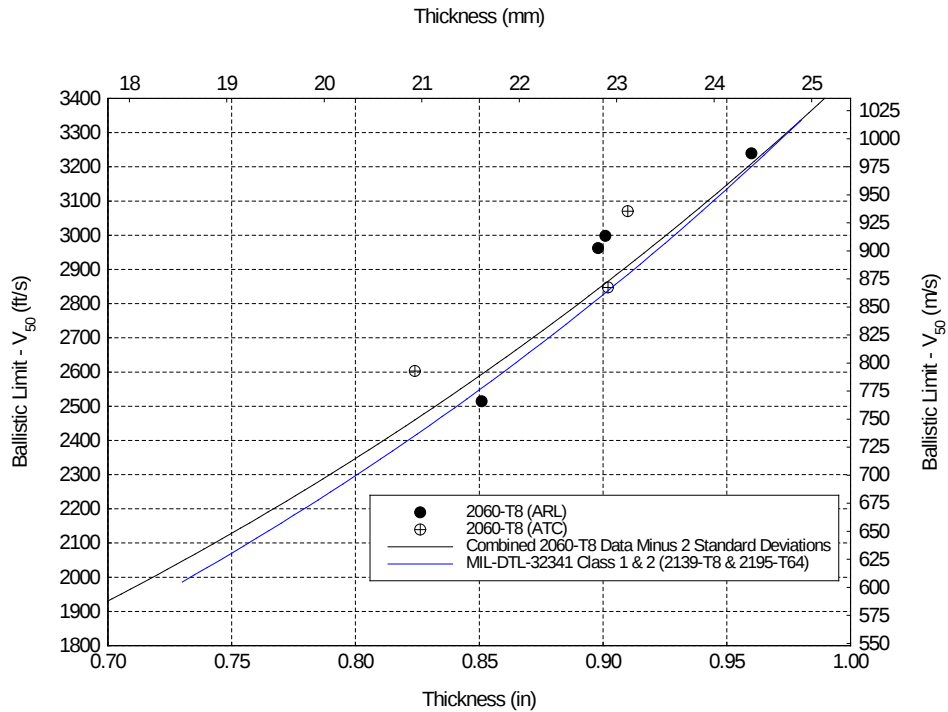


Fig. 7 Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 0.50-cal. FSP at 0° obliquity

Approved for public release; distribution is unlimited.

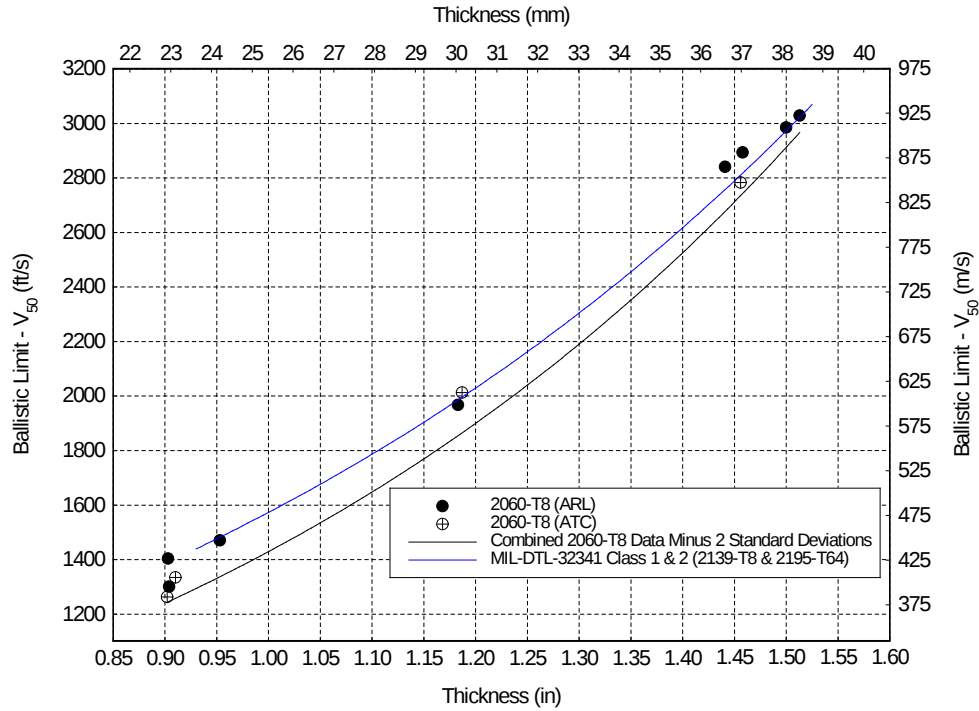


Fig. 8 Ballistic limit vs. thickness of AA2060 as compared with the existing specification for the 20-mm FSP at 0° obliquity

As can be observed in Figs. 4–6, the AP performance for AA2060 is higher than the existing AA2195 and AA2139 acceptance requirements against 0.30-cal. APM2. For the 0.50-cal. APM2, the performance is slightly higher than AA2139 and slightly lower than AA2195. Also note that the maximum thickness evaluated and qualified for AA2060 is 2.5 inches as compared with 2.25 inches for AA2195.

Examining the FSP performance (Figs. 7 and 8), it can be observed that the performance of AA2060 is not as well behaved as the AP data. The 0.50-cal. FSP performance yielded a $V_{50} - 2\sigma$ that was slightly higher than the existing specification but contained 2 data points that fell below that line. For the 20-mm FSP, AA2060 exhibited lower performance than AA2195 and AA2139. The performance gap is greater at lower thickness than higher ones.

The data collected by ARL, as well as data collected by ATC,⁷ were then used to generate acceptance tables for MIL-DTL-32341A (MR).¹ The acceptance velocities were calculated by fitting the V_{50} data minus 2 standard deviations with Eqs. 3 and 4 for AP and FSP projectiles, respectively.^{8,9}

$$V_A = 1000\sqrt{a + bt} \quad (3)$$

$$V_A = 1000e^{a+bt} \quad (4)$$

In Eqs. 3 and 4, V_A is the acceptance velocity, t is the actual thickness of the plate, and both a and b are constants of regression. Table 9 lists the constants of regression and the Pearson's R correlation coefficient for each projectile. The ballistic tables corresponding to the acceptance curves can be found in MIL-DTL-32341A (MR).¹

Table 9 Constants of regression for the acceptance curves for AA2060

Projectile type	6055		
	a	b	R
0.30-cal. APM2 at 30°	-0.902	7.17	0.977
0.30-cal. APM2 at 0°	-1.33	6.40	0.998
0.50-cal. APM2 at 0°	-1.06	3.60	0.997
0.50-cal. FSP at 0°	-0.711	1.96	0.869
20-mm FSP at 0°	-1.07	1.43	0.996

5. Conclusions

A ballistic evaluation has been performed on AA2060 in the T8 temper. This report has compared the performance of AA2060 against existing military-specification Al-armor material, namely AA2195 and AA2139. AA2060 performed better than AA2195 and AA2139 against the 0.30-cal. APM2 and demonstrated similar performance against the 0.50-cal. APM2. For FSP projectiles, AA2060 had similar performance to AA2195 and AA2139 against the 0.50-cal. FSP but exhibited some scattered data. For the 20-mm FSP, AA2060 had performance lower than that of AA2195 and AA2139, with a greater performance gap at lower thickness than with higher ones. This report has also documented the calculations used to derive the acceptance tables included in the updated military specification MIL-DTL-32341A (MR).

6. References

1. MIL-DTL-32341 (MR). Armor plate, aluminum, alloy 2139 weldable and alloy 2195 and 2060 unweldable appliqué. Aberdeen Proving Ground (MD): Army Research Laboratory (US); 2015 Apr 15.
2. International alloy designations and chemical composition limits for wrought aluminum and wrought aluminum alloys. Arlington (VA): The Aluminum Association, Inc.; 2009 Feb.
3. MIL-STD-662F. V₅₀ ballistic test for armor. Aberdeen Proving Ground (MD): Army Research Laboratory (US); 1997 Dec 18.
4. Grabarek C, Herr L. X-ray multi-flash system for measurement of projectile performance at the target. Aberdeen Proving Ground (MD): Army Ballistic Research Laboratory (US); 1966 Sep. Report No.: BRL-TN-1634.
5. Mascianica F. Ballistic technology of lightweight armor. Watertown (MA): Army Materials Research Agency (US); 1964 Sep. Report No.: AMRA MS 64-07.
6. MIL-DTL-46593B (MR). Projectile, calibers .22, .30, .50, and 20 mm fragment-simulating. Aberdeen Proving Ground (MD): Army Research Laboratory (US); 2008 Aug 11.
7. Beavers K. Unpublished data on 2060. Aberdeen Proving Ground (MD): Army Aberdeen Test Center (US); 2014 Dec 4.
8. DeLuca E, Anctil A. Laminate armor for light combat vehicles. Watertown (MA): Army Materials Technology Laboratory (US); 1986 Apr. Report No.: MTL TR 86-14.
9. Van Caneghem R, Typanski D, Latham R. Appendix C: ballistic testing of aluminum armor alloys – shock testing of weldments and specification data. Aberdeen Proving Ground (MD): Army Combat Systems Test Activity (US); 1986 Apr. Report No.: MTL TR 86-14.

INTENTIONALLY LEFT BLANK.

Appendix A. Ballistic Test Data: Individual Shot Results

This appendix appears in its original form, without editorial change.

Approved for public release; distribution is unlimited.

0.30-cal APM2

Target:	AA2060	Date:	8/20/2013
Plate Number:	215-014	Location:	EF 106
Thickness, in:	0.629		
Thickness, mm:	15.98		
Hardness, BHN:	159		
Obliquity:	30°		
Projectile:	0.30-cal AMP2		
Velocity Measurement:	Chrono		
V ₅₀ : 1921 ft/s		Number of Shots: 4	
Std Dev: 19 ft/s		Spread: 44 ft/s	
ZMR: N/A			
Striking Velocity		Pitch	Yaw
(ft/s)	(m/s)	(deg)	(deg)
			Result (PP/CP)
			Used for V ₅₀ (Yes/No)
			Shot Number
			Comments
1984	605	--	-- CP No 12960
1873	571	--	-- PP No 12961
1926	587	--	-- CP Yes 12962
1880	573	--	-- PP No 12963
1910	582	--	-- PP Yes 12964
1978	603	--	-- CP No 12965
1946	593	--	-- CP Yes 12966
1902	580	--	-- PP Yes 12967

Target:	AA2060				Date:	8/19/2013	
Plate Number:	215-016				Location:	EF 106	
Thickness, in:	0.678						
Thickness, mm:	17.22						
Hardness, BHN:	166						
Obliquity:	30°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2059 ft/s				Number of Shots: 4			
Std Dev: 19 ft/s				Spread: 43 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
1939	591	--	--	PP	No	12954	
2033	620	--	--	PP	Yes	12955	
2158	658	--	--	CP	No	12956	
2076	633	--	--	CP	Yes	12957	
2055	626	--	--	PP	Yes	12958	
2070	631	--	--	CP	Yes	12959	

Target:	AA2060				Date:	8/15/2013	
Plate Number:	425-801				Location:	EF 106	
Thickness, in:	0.851						
Thickness, mm:	21.62						
Hardness, BHN:	159						
Obliquity:	30°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2319 ft/s				Number of Shots: 4			
Std Dev: 14 ft/s				Spread: 33 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2323	708	--	--	CP	Yes	12946	
2211	674	--	--	PP	No	12947	
2269	692	--	--	PP	No	12948	
2250	686	--	--	PP	No	12949	
2303	702	--	--	PP	Yes	12950	
2314	705	--	--	PP	Yes	12951	
2369	722	--	--	CP	No	12952	
2336	712	--	--	CP	Yes	12953	

Target:	AA2060				Date:	8/14/2013	
Plate Number:	425-801				Location:	EF 106	
Thickness, in:	0.851						
Thickness, mm:	21.62						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2107 ft/s				Number of Shots: 4			
Std Dev: 22 ft/s				Spread: 48 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2095	639	--	--	PP	Yes	12940	
2188	667	--	--	CP	No	12941	
2068	630	--	--	PP	No	12942	
2120	646	--	--	CP	Yes	12943	
2083	635	--	--	PP	Yes	12944	
2131	649	--	--	CP	Yes	12945	

Target:	AA2060				Date:	8/13/2013	
Plate Number:	215-019				Location:	EF 106	
Thickness, in:	0.901						
Thickness, mm:	22.89						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2161 ft/s				Number of Shots: 4			
Std Dev: 30 ft/s				Spread: 57 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2188	667	--	--	CP	Yes	12935	
2111	643	--	--	PP	No	12936	
2186	666	--	--	CP	Yes	12937	
2140	652	--	--	PP	Yes	12938	
2131	649	--	--	PP	Yes	12939	

Target:	AA2060				Date:	8/8/2013	
Plate Number:	425-871				Location:	EF 106	
Thickness, in:	0.898						
Thickness, mm:	22.81						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2189 ft/s				Number of Shots: 4			
Std Dev: 26 ft/s				Spread: 57 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2262	689	--	--	CP	No	12928	
2242	683	--	--	CP	No	12929	
2107	642	--	--	PP	No	12930	
2174	663	--	--	PP	Yes	12931	
2225	678	--	--	CP	Yes	12932	
2187	667	--	--	CP	Yes	12933	
2168	661	--	--	PP	Yes	12934	

Target:	AA2060				Date:	8/7/2013	
Plate Number:	425-841				Location:	EF 106	
Thickness, in:	0.960						
Thickness, mm:	24.38						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2243 ft/s				Number of Shots: 4			
Std Dev: 29 ft/s				Spread: 60 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2135	651	--	--	PP	No	12920	
2313	705	--	--	CP	No	12921	
2188	667	--	--	PP	No	12922	
2228	679	--	--	PP	Yes	12923	
2269	692	--	--	CP	Yes	12924	
2209	673	--	--	PP	Yes	12925	
2295	699	--	--	CP	No	12926	
2265	690	--	--	CP	Yes	12927	

Target:	AA2060				Date:	8/26/2013	
Plate Number:	425-811				Location:	EF 106	
Thickness, in:	1.188						
Thickness, mm:	30.18						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2556 ft/s				Number of Shots: 6			
Std Dev: 36 ft/s				Spread: 88 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2563	781	--	--	PP	Yes	12984	
2603	793	--	--	CP	No	12985	
2582	787	--	--	CP	Yes	12986	
2520	768	--	--	PP	Yes	12987	
2575	785	--	--	CP	Yes	12988	
2504	763	--	--	PP	Yes	12989	
2592	790	--	--	CP	Yes	12990	

Target:	AA2060				Date:	8/21/2013	
Plate Number:	425-822				Location:	EF 106	
Thickness, in:	1.454						
Thickness, mm:	36.93						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ : 2916 ft/s				Number of Shots: 4			
Std Dev: 19 ft/s				Spread: 37 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2870	875	--	--	PP	No	12968	
2901	884	--	--	PP	Yes	12969	
2992	912	--	--	CP	No	12970	
2970	905	--	--	CP	No	12971	
2936	895	--	--	CP	Yes	12972	
2927	892	--	--	CP	Yes	12973	
2899	884	--	--	PP	Yes	12974	

Target:	AA2060				Date:	8/22/2013	
Plate Number:	425-852				Location:	EF 106	
Thickness, in:	1.441						
Thickness, mm:	36.60						
Hardness, BHN:	169						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ :		2884 ft/s			Number of Shots: 4		
Std Dev:		28 ft/s			Spread: 58 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2910	887	--	--	CP	Yes	12975	
2868	874	--	--	PP	Yes	12976	
2904	885	--	--	CP	Yes	12977	
2852	869	--	--	PP	Yes	12978	

Target:	AA2060			Date:	8/23/2013		
Plate Number:	215-012			Location:	EF 106		
Thickness, in:	1.500						
Thickness, mm:	38.10						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ :		2945 ft/s			Number of Shots: 4		
Std Dev:		26 ft/s			Spread: 58 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2974	906	--	--	CP	Yes	12979	
2884	879	--	--	PP	No	12980	
2916	889	--	--	PP	Yes	12981	
2931	893	--	--	PP	Yes	12982	
2958	902	--	--	CP	Yes	12983	

Target:	AA2060				Date:	8/6/2013	
Plate Number:	215-006				Location:	EF 106	
Thickness, in:	1.518						
Thickness, mm:	38.56						
Hardness, BHN:	170						
Obliquity:	0°						
Projectile:	0.30-cal AMP2						
Velocity Measurement:	Chrono						
V ₅₀ :		2972 ft/s			Number of Shots: 4		
Std Dev:		24 ft/s			Spread: 47 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2863	873	--	--	PP	No	12914	
2922	891	--	--	PP	No	12915	
2998	914	--	--	CP	Yes	12916	
2952	900	--	--	PP	Yes	12917	
2986	910	--	--	CP	Yes	12918	
2951	899	--	--	PP	Yes	12919	

0.50-cal APM2

Target:	AA2060				Date:	8/29/2013	
Plate Number:	425-822				Location:	EF 108	
Thickness, in:	1.454						
Thickness, mm:	36.93						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2132 ft/s				Number of Shots: 6			
Std Dev: 32 ft/s				Spread: 85 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2103	641	--	--	PP	Yes	11551	
2108	642	--	--	PP	Yes	11552	
2188	667	--	--	CP	Yes	11553	
2131	649	--	--	CP	Yes	11554	
2115	645	--	--	PP	Yes	11555	
2144	653	--	--	CP	Yes	11556	

Target:	AA2060				Date:	8/28/2013	
Plate Number:	425-852				Location:	EF 108	
Thickness, in:	1.441						
Thickness, mm:	36.60						
Hardness, BHN:	163						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2127 ft/s				Number of Shots: 4			
Std Dev: 17 ft/s				Spread: 38 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2079	634	--	--	PP	No	11545	
2144	653	--	--	CP	Yes	11546	
2088	636	--	--	PP	No	11547	
2106	642	--	--	PP	Yes	11548	
2122	647	--	--	PP	Yes	11549	
2135	651	--	--	CP	Yes	11550	

Target:	AA2060				Date:	8/27/2013	
Plate Number:	215-012				Location:	EF 108	
Thickness, in:	1.500						
Thickness, mm:	38.10						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2140 ft/s				Number of Shots: 4			
Std Dev: 18 ft/s				Spread: 43 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2166	660	--	--	CP	Yes	11539	
2072	632	--	--	PP	No	11540	
2102	641	--	--	PP	No	11541	
2136	651	--	--	CP	Yes	11542	
2123	647	--	--	PP	Yes	11543	
2135	651	--	--	PP	Yes	11544	

Target:	AA2060				Date:	8/26/2013	
Plate Number:	215-006				Location:	EF 108	
Thickness, in:	1.518						
Thickness, mm:	38.56						
Hardness, BHN:	170						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2164 ft/s				Number of Shots: 4			
Std Dev: 28 ft/s				Spread: 59 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2184	666	--	--	CP	Yes	11534	
2078	633	--	--	PP	No	11535	
2125	648	--	--	PP	Yes	11536	
2164	660	--	--	PP	Yes	11537	
2184	666	--	--	CP	Yes	11538	

Target:	AA2060				Date:	9/11/2013	
Plate Number:	425-821				Location:	EF 108	
Thickness, in:	1.955						
Thickness, mm:	49.66						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ :		2532 ft/s			Number of Shots: 4		
Std Dev:		21 ft/s			Spread: 45 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2509	765	--	--	PP	Yes	11586	
2544	775	--	--	CP	Yes	11587	
2521	768	--	--	PP	Yes	11588	
2554	778	--	--	CP	Yes	11589	

Target:	AA2060				Date:	9/10/2013	
Plate Number:	425-851				Location:	EF 108	
Thickness, in:	1.949						
Thickness, mm:	49.50						
Hardness, BHN:	163						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ :		2509 ft/s			Number of Shots: 4		
Std Dev:		24 ft/s			Spread: 51 ft/s		
ZMR:		2 ft/s					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2498	761	--	--	CP	Yes	11581	
2450	747	--	--	PP	No	11582	
2493	760	--	--	PP	Yes	11583	
2544	775	--	--	CP	Yes	11584	
2500	762	--	--	PP	Yes	11585	

Target:	AA2060				Date:	9/10/2013	
Plate Number:	425-881				Location:	EF 108	
Thickness, in:	1.956						
Thickness, mm:	49.68						
Hardness, BHN:	170						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ :		2517 ft/s			Number of Shots: 4		
Std Dev:		32 ft/s			Spread: 57 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2544	775	--	--	CP	Yes	11576	
2425	739	--	--	PP	No	11577	
2487	758	--	--	PP	Yes	11578	
2492	760	--	--	PP	Yes	11579	
2544	775	--	--	CP	Yes	11580	

Target:	AA2060				Date:	9/9/2013	
Plate Number:	215-011				Location:	EF 108	
Thickness, in:	2.165						
Thickness, mm:	54.99						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2646 ft/s				Number of Shots: 4			
Std Dev: 19 ft/s				Spread: 40 ft/s			
ZMR: 3 ft/s							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2675	815	--	--	CP	Yes	11572	
2635	803	--	--	PP	Yes	11573	
2636	803	--	--	CP	Yes	11574	
2639	804	--	--	PP	Yes	11575	

Target:	AA2060				Date:	9/5/2013	
Plate Number:	425-831				Location:	EF 108	
Thickness, in:	2.444						
Thickness, mm:	62.08						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2864 ft/s				Number of Shots: 4			
Std Dev: 13 ft/s				Spread: 33 ft/s			
ZMR: 1 ft/s							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2847	868	--	--	PP	Yes	11567	
2909	887	--	--	CP	No	11568	
2880	878	--	--	CP	Yes	11569	
2865	873	--	--	PP	Yes	11570	
2864	873	--	--	CP	Yes	11571	

Target:	AA2060				Date:	8/30/2013	
Plate Number:	425-861				Location:	EF 108	
Thickness, in:	2.431						
Thickness, mm:	61.75						
Hardness, BHN:	166						
Obliquity:	0°						
Projectile:	0.50-cal AMP2						
Velocity Measurement:	X-ray						
V ₅₀ : 2847 ft/s				Number of Shots: 6			
Std Dev: 36 ft/s				Spread: 85 ft/s			
ZMR: 35 ft/s							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2689	820	--	--	PP	No	11557	
2878	877	--	--	PP	Yes	11558	
2966	904	--	--	CP	No	11559	
2918	889	--	--	CP	No	11560	
2921	890	--	--	CP	No	11561	
2882	878	--	--	CP	Yes	11562	
2843	867	--	--	CP	Yes	11563	
2797	852	--	--	PP	Yes	11564	
2811	857	--	--	PP	Yes	11565	
2872	875	--	--	CP	Yes	11566	

0.50-cal FSP

Target:	AA2060	Date:	9/19/2013
Plate Number:	425-801	Location:	EF 108
Thickness, in:	0.851		
Thickness, mm:	21.62		
Hardness, BHN:	159		
Obliquity:	0°		
Projectile:	0.50-cal FSP		
Velocity Measurement:	Chrono		
V ₅₀ : 2514 ft/s		Number of Shots: 4	
Std Dev: 23 ft/s		Spread: 50 ft/s	
ZMR: N/A			
Striking Velocity		Pitch	Yaw
(ft/s)	(m/s)	(deg)	(deg)
			Result (PP/CP)
			Used for V ₅₀ (Yes/No)
			Shot Number
			Comments
2712	827	--	--
2519	768	--	--
2346	715	--	--
2459	749	--	--
2494	760	--	--
2499	762	--	--
2544	775	--	--

Target:	AA2060				Date:	9/18/2013	
Plate Number:	215-019				Location:	EF 108	
Thickness, in:	0.901						
Thickness, mm:	22.89						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	0.50-cal FSP						
Velocity Measurement:	Chrono						
V ₅₀ :		2998 ft/s			Number of Shots: 4		
Std Dev:		19 ft/s			Spread: 41 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2991	912	--	--	CP	Yes	11612	
2924	891	--	--	PP	No	11613	
2985	910	--	--	PP	Yes	11614	
3026	922	--	--	CP	Yes	11615	
3033	924	--	--	CP	No	11616	
2929	893	--	--	PP	No	11617	
2988	911	--	--	PP	Yes	11618	

Target:	AA2060				Date:	9/17/2013	
Plate Number:	425-871				Location:	EF 108	
Thickness, in:	0.898						
Thickness, mm:	22.81						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	0.50-cal FSP						
Velocity Measurement:	Chrono						
V ₅₀ : 2962 ft/s				Number of Shots: 4			
Std Dev: 21 ft/s				Spread: 49 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2814	858	--	--	PP	No	11603	
2834	864	--	--	PP	No	11604	
2931	893	--	--	PP	No	11605	
3044	928	--	--	CP	No	11606	
2968	905	--	--	CP	Yes	11607	
2934	894	--	--	PP	Yes	11608	
2964	903	--	--	PP	Yes	11609	
3025	922	--	--	CP	No	11610	
2983	909	--	--	CP	Yes	11611	

Target:	AA2060				Date:	9/16/2013	
Plate Number:	425-841				Location:	EF 108	
Thickness, in:	0.960						
Thickness, mm:	24.38						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	0.50-cal FSP						
Velocity Measurement:	Chrono						
V ₅₀ : 3239 ft/s				Number of Shots: 6			
Std Dev: 35 ft/s				Spread: 87 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
3282	1000	--	--	CP	Yes	11596	
3144	958	--	--	PP	No	11597	
3262	994	--	--	CP	Yes	11598	
3195	974	--	--	PP	Yes	11599	
3213	979	--	--	PP	Yes	11600	
3218	981	--	--	PP	Yes	11601	
3265	995	--	--	CP	Yes	11602	

20-mm FSP

Target:	AA2060				Date:	9/26/2013	
Plate Number:	215-019				Location:	EF 110G	
Thickness, in:	0.903						
Thickness, mm:	22.94						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ : 1401 ft/s				Number of Shots: 10			
Std Dev: 56 ft/s				Spread: 151 ft/s			
ZMR: 79 ft/s							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
1462	446	--	--	PP	Yes	14557	
1485	453	--	--	CP	No	14558	
1449	442	--	--	CP	Yes	14559	
1479	451	--	--	CP	Yes	14560	
1453	443	--	--	CP	Yes	14561	
1383	422	--	--	CP	Yes	14562	
1304	397	--	--	PP	No	14563	
1328	405	--	--	PP	Yes	14564	
1341	409	--	--	PP	Yes	14565	
1346	410	--	--	PP	Yes	14566	
1361	415	--	--	PP	Yes	14567	
1403	415	--	--	CP	Yes	14568	

Target:	AA2060				Date:	9/27/2013	
Plate Number:	425-871				Location:	EF 110G	
Thickness, in:	0.904						
Thickness, mm:	22.96						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		1298 ft/s			Number of Shots: 4		
Std Dev:		16 ft/s			Spread: 34 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
1481	451	--	--	CP	No	14569	
1361	415	--	--	CP	No	14570	
1262	385	--	--	PP	No	14571	
1138	347	--	--	PP	No	14572	
1274	388	--	--	PP	Yes	14573	
1303	397	--	--	PP	Yes	14574	
1308	399	--	--	CP	Yes	14575	
1305	398	--	--	CP	Yes	14576	

Target:	AA2060				Date:	9/30/2013	
Plate Number:	425-841				Location:	EF 110G	
Thickness, in:	0.953						
Thickness, mm:	24.21						
Hardness, BHN:	163						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		1468 ft/s			Number of Shots: 4		
Std Dev:		17 ft/s			Spread: 38 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
1681	512	--	--	CP	No	14579	
1566	477	--	--	CP	No	14580	
1532	467	--	--	CP	No	14581	
1456	444	--	--	PP	Yes	14582	
1490	454	--	--	CP	Yes	14583	
1472	449	--	--	CP	Yes	14584	
1452	443	--	--	PP	Yes	14585	

Target:	AA2060				Date:	10/1/2013	
Plate Number:	425-811				Location:	EF 110G	
Thickness, in:	1.183						
Thickness, mm:	30.05						
Hardness, BHN:	159						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		1965 ft/s			Number of Shots: 4		
Std Dev:		19 ft/s			Spread: 44 ft/s		
ZMR:		0 ft/s					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2026	617	--	--	CP	No	14586	
1937	590	--	--	PP	Yes	14587	
1971	601	--	--	PP	Yes	14588	
1971	601	--	--	CP	Yes	14589	
1981	604	--	--	CP	Yes	14590	

Target:	AA2060				Date:	10/2/2013	
Plate Number:	425-822				Location:	EF 110G	
Thickness, in:	1.458						
Thickness, mm:	37.03						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		2892 ft/s			Number of Shots: 4		
Std Dev:		25 ft/s			Spread: 50 ft/s		
ZMR:		0 ft/s					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2685	818	--	--	PP	No	14592	
2880	878	--	--	PP	Yes	14593	
2929	893	--	--	CP	Yes	14594	
2879	877	--	--	CP	Yes	14595	
2879	877	--	--	PP	Yes	14596	

Target:	AA2060				Date:	10/3/2013	
Plate Number:	425-852				Location:	EF 110G	
Thickness, in:	1.441						
Thickness, mm:	36.60						
Hardness, BHN:	163						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ : 2839 ft/s				Number of Shots: 4			
Std Dev: 17 ft/s				Spread: 35 ft/s			
ZMR: 35 ft/s							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
2898	883	--	--	CP	No	14597	
2848	868	--	--	CP	Yes	14598	
2814	858	--	--	CP	Yes	14599	
2793	851	--	--	PP	No	14600	
2800	853	--	--	PP	No	14601	
2844	867	--	--	PP	Yes	14602	
2849	868	--	--	PP	Yes	14603	

Target:	AA2060				Date:	10/8/2013	
Plate Number:	215-012				Location:	EF 110G	
Thickness, in:	1.500						
Thickness, mm:	38.10						
Hardness, BHN:	170						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		2983 ft/s			Number of Shots: 4		
Std Dev:		22 ft/s			Spread: 54 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
3013	918	--	--	CP	Yes	14608	
2982	909	--	--	CP	Yes	14609	
2959	902	--	--	PP	Yes	14610	
2979	908	--	--	PP	Yes	14611	

Target:	AA2060				Date:	10/9/2013	
Plate Number:	215-006				Location:	EF 110G	
Thickness, in:	1.513						
Thickness, mm:	38.43						
Hardness, BHN:	163						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		3027 ft/s			Number of Shots: 4		
Std Dev:		3 ft/s			Spread: 8 ft/s		
ZMR:		2 ft/s					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
3101	945	--	--	CP	No	14612	
3071	936	--	--	CP	No	14613	
2995	913	--	--	PP	No	14614	
2992	912	--	--	PP	No	14615	
3031	924	--	--	CP	Yes	14616	
3023	921	--	--	PP	Yes	14617	
2955	901	--	--	PP	No	14618	
3028	923	--	--	PP	Yes	14619	
3026	922	--	--	CP	Yes	14620	

Target:	AA2060				Date:	10/6/2013	
Plate Number:	425-821				Location:	EF 110G	
Thickness, in:	1.950						
Thickness, mm:	49.53						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ : 3979 ft/s				Number of Shots: 4			
Std Dev: 21 ft/s				Spread: 49 ft/s			
ZMR: N/A							
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
3093	943	--	--	PP	No	14621	
3219	981	--	--	PP	No	14622	
3386	1032	--	--	PP	No	14623	
4771	1454	--	--	CP	No	14628	
4527	1380	--	--	CP	No	14629	
4425	1349	--	--	N/A	No	14630	FSP hit stripper plate - No test
4447	1355	--	--	CP	No	14631	
4346	1325	--	--	CP	No	14632	
4149	1265	--	--	CP	No	14633	
4063	1238	--	--	CP	No	14634	
3907	1191	--	--	PP	No	14635	
3954	1205	--	--	PP	Yes	14636	
4029	1228	--	--	CP	No	14637	
4003	1220	--	--	CP	Yes	14638	
3973	1211	--	--	PP	Yes	14639	
3987	1215	--	--	CP	Yes	14640	

Target:	AA2060				Date:	10/23/2013	
Plate Number:	425-851				Location:	EF 110G	
Thickness, in:	1.950						
Thickness, mm:	49.53						
Hardness, BHN:	156						
Obliquity:	0°						
Projectile:	20-mm FSP						
Velocity Measurement:	X-ray						
V ₅₀ :		4047 ft/s			Number of Shots: 6		
Std Dev:		25 ft/s			Spread: 70 ft/s		
ZMR:		N/A					
Striking Velocity		Pitch (deg)	Yaw (deg)	Result (PP/CP)	Used for V ₅₀ (Yes/No)	Shot Number	Comments
(ft/s)	(m/s)						
3957	1206	0.75	-0.25	PP	No	14641	
4145	1263	0.00	-0.25	CP	No	14642	
4142	1262	0.25	-0.25	CP	No	14643	
4021	1226	1.00	1.25	PP	Yes	14644	
4091	1247	0.25	0.00	CP	No	14645	
4091	1247	1.00	-0.75	PP	Yes	14646	
4118	1255	0.00	-0.50	CP	No	14647	
4038	1231	-0.25	0.00	CP	Yes	14648	
4053	1235	-0.25	1.25	CP	Yes	14649	
4050	1234	1.25	-0.25	CP	Yes	14650	
4026	1227	0.75	0.25	PP	Yes	14651	

INTENTIONALLY LEFT BLANK.

Appendix B. Additional Ballistic Test Data

The following tables list data collected by Aberdeen Test Center.¹

Table B-1 APM2 0.30-cal., 30° obliquity ballistic performance

Plate ID	Nominal thickness		Actual thickness		Areal density		Ballistic limit		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(psf)	(m/s)	(fps)	(m/s)	(fps)
215-014	15.88	0.63	16.13	0.635	43.75	8.96	590	1,935	6	21
215-016	15.88	0.63	17.35	0.683	47.05	9.64	607	1,990	7	23

Table B-2 APM2 0.30-cal., 0° obliquity ballistic performance

Plate ID	Nominal thickness		Actual thickness		Areal density		Ballistic limit		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(psf)	(m/s)	(fps)	(m/s)	(fps)
425-811	28.58	1.13	30.15	1.187	81.77	16.75	781	2,564	5	16
425-801	22.23	0.88	20.93	0.824	56.77	11.63	636	2,088	3	9
215-019	22.23	0.88	23.11	0.910	62.69	12.84	671	2,200	8	25
425-871	22.23	0.88	22.91	0.902	62.14	12.73	662	2,171	9	31
425-822	38.10	1.50	36.98	1.456	100.30	20.54	887	2,910	8	26

Table B-3 APM2 0.50-cal., 0° obliquity ballistic performance

Plate ID	Nominal thickness		Actual thickness		Areal density		Ballistic limit		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(psf)	(m/s)	(fps)	(m/s)	(fps)
425-882	63.50	2.50	62.99	2.480	170.85	34.99	872	2,860	5	18
425-831	63.50	2.50	62.15	2.447	168.58	34.53	874	2,868	5	18
425-881	50.80	2.00	49.86	1.963	135.23	27.70	766	2,512	5	16
425-821	50.80	2.00	49.78	1.960	135.03	27.66	764	2,506	8	25
215-011	53.98	2.13	54.84	2.159	148.73	30.46	820	2,690	7	23
425-822	38.10	1.50	36.98	1.456	100.30	20.54	642	2,108	5	16

Table B-4 0.50-cal. FSP, 0° obliquity ballistic performance

Plate ID	Nominal thickness		Actual thickness		Areal density		Ballistic limit		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(psf)	(m/s)	(fps)	(m/s)	(fps)
425-811	28.58	1.13	30.15	1.187	81.77	16.75	1,259	4,132	2	7
215-014	15.88	0.63	16.13	0.635	43.75	8.96	502	1,646	4	13
215-016	15.88	0.63	17.35	0.683	47.05	9.64	531	1,743	6	21
425-801	22.23	0.88	20.93	0.824	56.77	11.63	793	2,603	7	24
215-019	22.23	0.88	23.11	0.910	62.69	12.84	936	3,070	5	18
425-871	22.23	0.88	22.91	0.902	62.14	12.73	868	2,847	7	23

¹MIL-DTL-32341 (MR). Armor plate, aluminum, alloy 2139 weldable and alloy 2195 and 2060 unweldable appliqué. Aberdeen Proving Ground (MD): Army Research Laboratory (US); 2015 Apr 15.

Table B-5 FSP 20-mm, 0° obliquity ballistic performance

Plate ID	Nominal thickness		Actual thickness		Areal density		Ballistic limit		Standard deviation	
	(mm)	(inches)	(mm)	(inches)	(kg/m ²)	(psf)	(m/s)	(fps)	(m/s)	(fps)
425-811	28.58	1.13	30.15	1.187	81.77	16.75	613	2,010	7	24
215-019	22.23	0.88	23.11	0.910	62.69	12.84	406	1,332	7	24
425-871	22.23	0.88	22.91	0.902	62.14	12.73	384	1,260	5	16
425-881	50.80	2.00	49.86	1.963	135.23	27.70	1237	4,058	8	26
425-821	50.80	2.00	49.78	1.960	135.03	27.66	1203	3,948	8	26
215-011	53.98	2.13	54.84	2.159	148.73	30.46	1356	4,450	9	29
425-822	38.10	1.50	36.98	1.456	100.30	20.54	848	2,781	8	27

INTENTIONALLY LEFT BLANK.

List of Symbols, Abbreviations, and Acronyms

AA	aluminum alloy
Al	aluminum
AP	armor-piercing
ARL	US Army Research Laboratory
ATC	Aberdeen Test Center
CP	complete penetration
DAC	Defense Acquisition Challenge
EF	experimental facility
FSP	fragment-simulating projectile
IR	infrared
OSD	US Office of the Secretary of Defense
PP	partial penetration

1 (PDF)	DEFENSE TECHNICAL INFORMATION CTR DTIC OCA	1 (PDF)	PEO GCS D SPENSER
2 (PDF)	DIRECTOR US ARMY RESEARCH LAB RDRL CIO LL IMAL HRA MAIL & RECORDS MGMT	1 (PDF)	OSHKOSH DEFENSE M RICHMOND
3 (PDF)	ALCOA R KANE D MOOY J CARATELLI	2 (PDF)	RDECOM W EVERETT R IMPERIALE
1 (PDF)	ALERIS L KRAMER	2 (PDF)	OFC OF THE DPTY ASSIST SECY OF DEFNS FOR EMERGING CAPABILITY & PROTOTYPING E WYATT R THOMPSON
3 (PDF)	CONSTELLIUM P KOBE M NIEDZINSKI M PHILBROOK	1 (PDF)	US NAVY RSRCH LAB J MORAN
1 (PDF)	KAISER J SCHEURING	1 (PDF)	NSWC CARDEROCK DIV E TRUEMAN
1 (PDF)	NSWC R PETERSON	2 (PDF)	DOD CORROSION POLICY AND OVERSIGHT OFC R HAYS D DUNMIRE
4 (PDF)	BAE SYSTEMS J DORSCH B KARIYA D SCHADE M MIDDIONE	1 (PDF)	OFC OF THE DIR DEFNS RSRCH AND ENGRG L SLOTER
1 (PDF)	GDLS W HERMAN	1 (PDF)	USMC CORROSION PREVENTION AND CONTROL A SHEETZ
1 (PDF)	WA GOOCH CONSULTING INC W GOOCH	48 (PDF)	DIR USARL RDRL WML P PEREGINO RDRL WML H L MAGNESS T EHLERS J NEWILL RDRL WMM R DOWDING H MAUPIN RDRL WMM C B PLACZANKIS RDRL WMM D B CHEESEMAN R SQUILLACIOTI R CARTER M KORNECKI RDRL WMM F K DOHERTY
2 (PDF)	ATEC K BEAVERS J WHITE		
8 (PDF)	TARDEC A SOCKS J PEREZ F RICKERT C FILAR R TRANCYGIER M MCDONNEL M ROGERS D TZELEPIS		

J CHINELLA
E Klier
S GRENDahl
RDRL WMP D
J RUNYEON
D KLEPONIS
D PETTY
M KEELE
RDRL WMP E
P BARTKOWSKI
S BARTUS
M BURKINS
D CHURN
P DAVIS
B DAWSON
A DUCOTE
K DUDECK
D GALLARDY
D HACKBARTH
D HANDSHOE
J HOGAN
D HORNBAKER
E HORWATH
J HOUSKAMP
T JONES
M KLUSEWITZ
C KRAUTHAUSER
D LITTLE
K MCNAB
J MONTGOMERY
T O'CONNOR
T QUIGG
D SCHALL
D SHOWALTER
N STURGILL
P SWOBODA
C WALTER
RDRL WMP F
N GNIAZDOWSKI

INTENTIONALLY LEFT BLANK.