



AFRL-RX-WP-JA-2016-0279

**A TWO-STEP APPROACH FOR PRODUCING AN
ULTRAFINE-GRAIN STRUCTURE IN Cu-30Zn BRASS
(POSTPRINT)**

**Tatyana Konkova, Sergey Mironov, Alexander Korznikov, and Galia Korznikova,
and Mikhail Myshlyaev**

Russian Academy of Science

Sergey Mironov

Tohoku University

Lee Semiatin

AFRL/RX

**13 August 2015
Interim Report**

**Distribution Statement A.
Approved for public release: distribution unlimited.**

© 2015 ELSEVIER LTD

**(STINFO COPY)
AIR FORCE RESEARCH LABORATORY
MATERIALS AND MANUFACTURING DIRECTORATE
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7750
AIR FORCE MATERIEL COMMAND
UNITED STATES AIR FORCE**

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

1. REPORT DATE (DD-MM-YY) 13 August 2015		2. REPORT TYPE Interim		3. DATES COVERED (From - To) 19 March 2014 – 13 July 2015	
4. TITLE AND SUBTITLE A TWO-STEP APPROACH FOR PRODUCING AN ULTRAFINE-GRAIN STRUCTURE IN Cu-30Zn BRASS (POSTPRINT)				5a. CONTRACT NUMBER IN-HOUSE	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) 1) Tatyana Konkova, Sergey Mironov, Alexander Korznikov, and Galia Korznikova, and Mikhail Myshlyaev – Russian Academy of Science 2) Sergey Mironov – Tohoku University (continued on page 2)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER X0W6	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) 1) Russian Academy of Science, 39 KhalturinStr., Ufa 450001, Russia 2) Tohoku University, 6-6-02 Aramaki-aza-Aoba, Sendai 980-8579, Japan (continued on page 2)				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory Materials and Manufacturing Directorate Wright-Patterson Air Force Base, OH 45433-7750 Air Force Materiel Command United States Air Force				10. SPONSORING/MONITORING AGENCY ACRONYM(S) AFRL/RXCM	
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S) AFRL-RX-WP-JA-2016-0279	
12. DISTRIBUTION/AVAILABILITY STATEMENT Distribution Statement A. Approved for public release: distribution unlimited.					
13. SUPPLEMENTARY NOTES PA Case Number: 88ABW-2015-3975; Clearance Date: 13Aug 2015. This document contains color. Journal article published in Materials Letters, Vol. 161, 15 Dec 2015. © 2015 Elsevier Ltd. The U.S. Government is joint author of the work and has the right to use, modify, reproduce, release, perform, display, or disclose the work. The final publication is available at www.elsevier.com/locate/matlet http://dx.doi.org/10.1016/j.matlet.2015.08.025					
14. ABSTRACT (Maximum 200 words) A two-step approach involving cryogenic rolling and subsequent recrystallization annealing was developed to produce an ultrafine-grain structure in Cu-30Zn brass. The material so processed was characterized by a mean grain size of 0.5 μm, fraction of high-angle boundaries of 90 pct., a weak crystallographic texture, and strength twice that of initial material.					
15. SUBJECT TERMS Copper alloys; Cryogenic deformation; Grain refinement; Electron backscatter diffraction; Microstructure; Texture					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT: SAR	18. NUMBER OF PAGES 7	19a. NAME OF RESPONSIBLE PERSON (Monitor) Bill Song 19b. TELEPHONE NUMBER (Include Area Code) (937) 255-1351
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			

REPORT DOCUMENTATION PAGE Cont'd

6. AUTHOR(S)

3) Lee Semiatin – AFRL/RX

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

3) AFRL/RX
Wright-Patterson AFB, OH 45433



ELSEVIER

Contents lists available at ScienceDirect

Materials Letters

journal homepage: www.elsevier.com/locate/matlet

A two-step approach for producing an ultrafine-grain structure in Cu–30Zn brass



Tatyana Konkova^a, Sergey Mironov^{a,b,*}, Alexander Korznikov^a, Galia Korznikova^a, Mikhail Myshlyaev^{c,d}, Lee Semiatin^e

^a Institute for Metals Superplasticity Problems, Russian Academy of Science, 39 Khalturin Str., Ufa 450001, Russia

^b Department of Materials Processing, Graduate School of Engineering, Tohoku University, 6-6-02 Aramaki-aza-Aoba, Sendai 980-8579, Japan

^c Baikov Institute of Metallurgy and Material Science, Russian Academy of Science, 49 Lenin-av., Moscow 119991, Russia

^d Institute of Solid State Physics, Russian Academy of Sciences, 2 Academic Osypian Str., Chernogolovka, Moscow Oblast 142432, Russia

^e Air Force Research Laboratory, Materials and Manufacturing Directorate, AFRL/RXCM, Wright-Patterson AFB, OH 45433-7817, USA

ARTICLE INFO

Article history:

Received 30 July 2015

Received in revised form

3 August 2015

Accepted 4 August 2015

Available online 13 August 2015

Keywords:

Copper alloys

Cryogenic deformation

Grain refinement

Electron backscatter diffraction

Microstructure

Texture

ABSTRACT

A two-step approach involving cryogenic rolling and subsequent recrystallization annealing was developed to produce an ultrafine-grain structure in Cu–30Zn brass. The material so processed was characterized by a mean grain size of 0.5 μm , fraction of high-angle boundaries of 90 pct., a weak crystallographic texture, and strength twice that of initial material.

© 2015 Elsevier B.V. All rights reserved.

1. Introduction

Large deformation at cryogenic temperatures is sometimes considered as a simple and cost-effective technique for producing bulk ultrafine-grain materials [1–8]. For a number of alloys, the grain-refinement efficiency of this method is related to the enhancement of mechanical twinning and shear banding. Due to the sensitivity of these mechanisms to crystallographic orientation, however, the microstructures so produced may be extremely inhomogeneous [7,8]. One way to overcome this problem and thereby develop a more homogeneous ultrafine-grain structure may be recrystallization annealing following cryogenic deformation. In this regard, the energy stored in cryo-deformed materials tends to be large, and hence the size of recrystallization nuclei may be within the ultrafine-grain (UFG) range ($\leq 1 \mu\text{m}$). A recrystallization treatment may also be effective in promoting grain refinement for materials prone to annealing twinning. To examine

the feasibility of such a two-step approach, microstructure response in Cu–30Zn brass subjected to cryogenic rolling and subsequent recrystallization annealing was determined in the present work.

2. Experiment

The program material was manufactured by ingot casting. Preforms extracted from the ingot were rolled cryogenically to 90 pct. overall thickness reduction (true strain = -2.3) using multiple passes of ~ 10 pct. each. To provide cryogenic-deformation conditions, the rolling perform and work rolls were soaked in liquid nitrogen prior to each pass and held for 20 min; immediately after each pass, the workpiece was re-inserted into liquid nitrogen. The typical flat-rolling convention was adopted in this work; i.e., the rolling, long-transverse, and thickness/normal directions were denoted as RD, TD, and ND, respectively. Following cryo-rolling, small sections of the sheet were given a recrystallization anneal at 400 °C ($\sim 0.55T_m$, where T_m is the melting point) for times ranging from 1 min to 10 hours, followed by water quenching; an additional specimen was quenched immediately

* Corresponding author at: Department of Materials Processing, Graduate School of Engineering, Tohoku University, 6-6-02 Aramaki-aza-Aoba, Sendai 980-8579, Japan. Fax: +81 22 795 7352.

E-mail address: S-72@mail.ru (S. Mironov).

<http://dx.doi.org/10.1016/j.matlet.2015.08.025>

0167-577X/© 2015 Elsevier B.V. All rights reserved.

upon reaching 400 °C. The final microstructures were characterized primarily by an electron back-scatter diffraction (EBSD) technique. In all cases, the mid-thickness rolling plane (containing the RD and TD) was examined. To eliminate spurious boundaries caused by orientation noise, a lower limit boundary-misorientation cutoff of 2° was used. A 15° criterion was employed to differentiate low-angle boundaries (LABs) and high-angle boundaries (HABs).

3. Results and discussion

The effect of the two-step treatment on microstructure is summarized in Fig. 1. In the starting material, the microstructure was dominated by millimeter-scale dendrites containing poorly-developed substructure (Fig. 1a). Cryogenic rolling yielded significant grain refinement, but the microstructure so-produced was very heterogeneous (Fig. 1b). To a first approximation, it could be described in terms of coarse remnants of original dendrites intermixed with ultrafine-grain domains. The latter regions consisted of shear bands, mechanical twins, and a dense LAB substructure. As indicated Fig. 1c, subsequent recrystallization greatly improved microstructure uniformity. The mean grain size (including twin boundaries) was rather fine, i.e., ~0.5 μm (Fig. 2a), thus lying within the ultrafine-grain regime. Hence, cryogenic rolling coupled with low-temperature recrystallization annealing may indeed be used to produce an ultrafine structure in Cu–30Zn brass. Equally important, the recrystallized microstructure did not coarsen substantially during relatively long-term soaking at 400 °C (Fig. 2a), thus suggesting a reasonably-wide processing window for the annealing treatment.

Remarkably, the cryo-rolled material was completely recrystallized during the heat-up stage of the annealing treatment; i.e., prior to the isothermal hold at the peak annealing temperature. The rapid transformation of the heavily-deformed material was related presumably to the high density of defects (vacancies, in particular) which enhanced the diffusion-controlled processes. A somewhat similar effect has been recently observed in severely-deformed copper-base alloys by Straumal et al. [9,10] who reported phase transformations at *ambient* temperature.

Not surprisingly, the final recrystallized material contained a

significant proportion of annealing twins. Accordingly, the grain-size distribution was bimodal, consisting of a twin-related peak at ~0.1 μm and a grain-related peak at ~1 μm (Fig. 2b). These measurements indicated that the formation of annealing twins was the key mechanism providing grain refinement to the ultrafine-grain range.

The fraction of high-angle boundaries in the final recrystallized material was measured to be ~90 pct. (Fig. 2c). It is noteworthy that ~50 pct. of the grain-boundary area comprised twin-induced Σ3 and Σ9 misorientations with their characteristic peaks near 60° and 39°, respectively, in the misorientation-angle distribution and corresponding rotation axes near <111> and <110> poles in the misorientation-angle plot (Fig. 2c).

The final recrystallized material was characterized by a relatively weak (~3 × random) crystallographic texture (Fig. 3). The texture included several dominant components; i.e., the S {011} <634>, Q {013} <231>, Brass {011} <112>, and Dillamore {4, 4, 11} <11, 11, 8> orientations (Table 1). The Brass and S components have been attributed to cryogenic rolling [7,8], whereas the source of the other orientations is not clear and requires further study.

The effect of the two-step treatment on the room-temperature hardness is summarized in Fig. 4. Cryogenic rolling almost tripled the microhardness relative to the as-received, as-cast condition. The pronounced material strengthening was likely related to the large degree of grain refinement associated with HABs and LABs (Fig. 1b) as well as the retention of dislocation substructure that led to work hardening. The subsequent recrystallization anneal resulted in ~30 pct. reduction in hardness (Fig. 4). In view of the concurrent grain refinement during recrystallization (Fig. 1c), the observed softening was likely associated with the elimination of dislocation substructure. Nevertheless, the strength of the final recrystallized material was still twice that of the as-received, as-cast material.

4. Conclusion

In conclusion, a relatively-simple two-step approach for producing an ultrafine-grain structure in Cu–30Zn brass was established. The proposed method comprised cryogenic rolling to 90-pct. thickness reduction followed by recrystallization annealing at

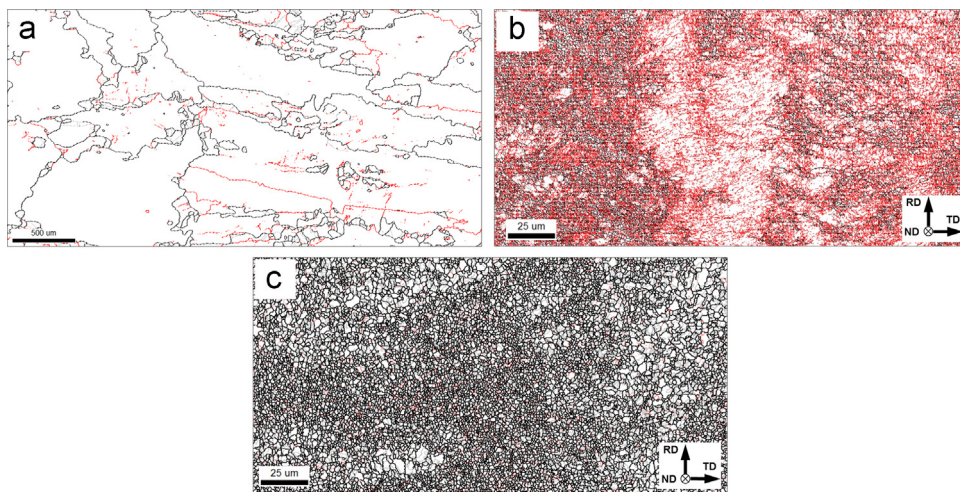


Fig. 1. EBSD maps showing the microstructure of Cu–30Zn (a) in the as-received condition, (b) after cryogenic rolling to 90 pct. thickness reduction, and (c) after rolling and subsequent recrystallization heat treatment. In the maps, LABs, HABs, and Σ3 twin boundaries are depicted as red, black, and gray lines, respectively. RD, TD and ND are rolling direction, transverse direction, and normal direction, respectively. Note the difference in magnification in the EBSD maps.

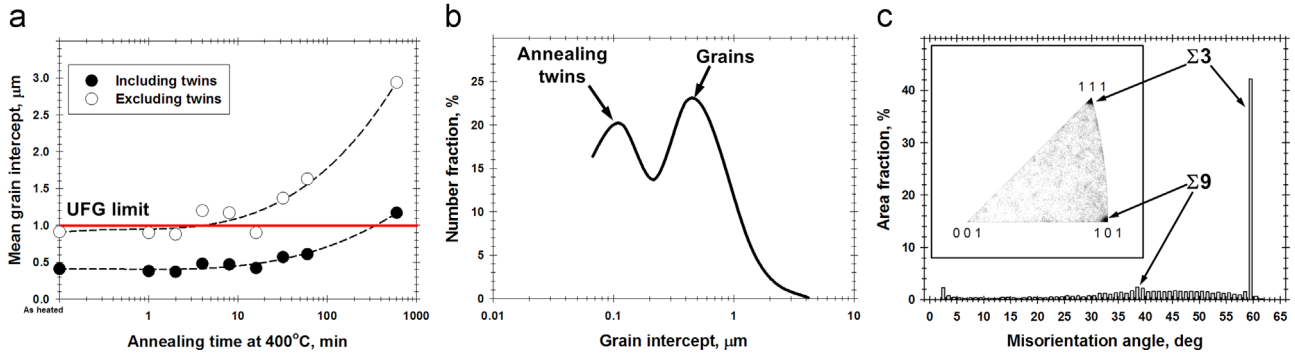


Fig. 2. (a) Effect of recrystallization time on mean grain size and (b, c) typical grain-size and misorientation distributions in the final recrystallized condition. The misorientation-axis distribution is shown as an inset in (c).

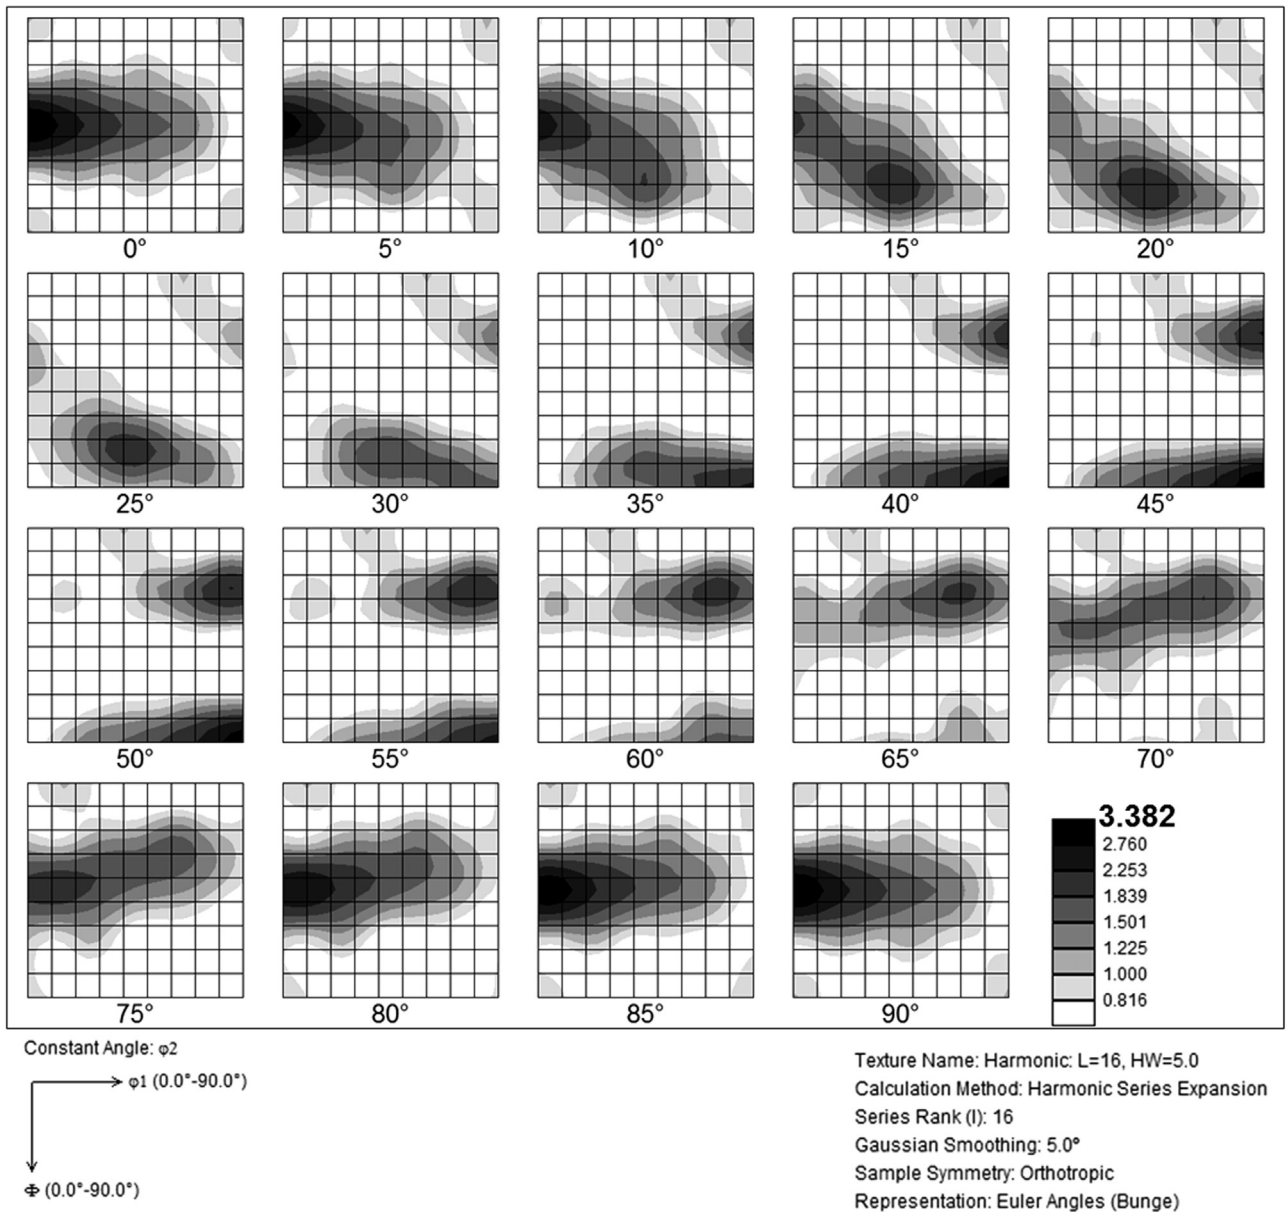


Fig. 3. Typical orientation-distribution function of the final recrystallized material.

Table 1
Volume fraction of texture components (within 15° tolerance) in recrystallized material.

Notation	Miller indices	Euler angles ($\varphi_1, \Phi, \varphi_2$)	Fraction, %
Deformation texture			
Goss	{011}<100>	(0, 45, 90)	4.3
Brass	{011}<112>	(35, 45, 90)	7.8
Dillamore	{4,4,11}<11,11,8>	(90, 27, 45)	6.8
S	{123}<634>	(59, 37, 63)	9.9
Recrystallization texture			
Cube	{001}<100>	(0, 0, 0)	2.0
P	{011}<122>	(70, 45, 0)	4.5
Q	{013}<231>	(58, 18, 0)	8.0

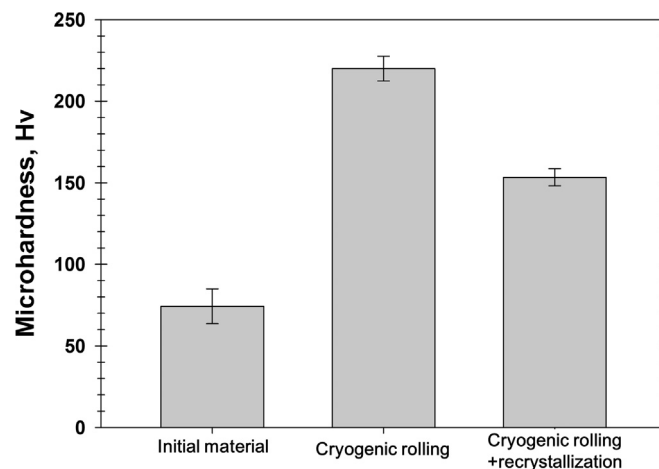


Fig. 4. Effect of two-step treatment on microhardness.

400 °C (0.55 T_m). The final microstructure produced by this means was characterized by a mean line-intercept length of $\sim 0.5 \mu\text{m}$, HAB proportion of 90 pct. (with a fraction of annealing-twin boundaries of ~ 50 pct.), and a weak crystallographic texture. The pronounced grain refinement induced by the two-step process doubled the material strength. The proposed technology may also be suitable for grain refinement in other materials with low stacking-fault energy.

Acknowledgments

Financial support from the Russian Fund for Fundamental Research (Project no. 14-02-97004) is gratefully acknowledged. The authors also thank P. Klassman for assistance during cryogenic rolling.

References

- [1] Y. Huang, P.B. Prangnell, The effect of cryogenic temperature and change in deformation mode on the limiting grain size in a severely deformed dilute aluminum alloy, *Acta Mater.* 56 (2008) 1619–1632, <http://dx.doi.org/10.1016/j.actamat.2007.12.017>.
- [2] T. Konkova, S. Mironov, A. Korznikov, S.L. Semiatin, Microstructural response of pure copper to cryogenic rolling, *Acta Mater.* 58 (2010) 5262–5273, <http://dx.doi.org/10.1016/j.actamat.2010.05.056>.
- [3] S.V. Zhrebtsov, G.S. Dyakonov, A.A. Salem, V.I. Sokolenko, G.A. Salishchev, S. L. Semiatin, Formation of nanostructures in commercial-purity titanium via cryorolling, *Acta Mater.* 61 (2013) 1167–1178, <http://dx.doi.org/10.1016/j.actamat.2012.10.026>.
- [4] G.H. Xiao, N.R. Tao, K. Lu, Microstructures and mechanical properties of a Cu–Zn alloy subjected to cryogenic dynamic plastic deformation, *Mater. Sci. Eng. A* 513–514 (2009) 13–21, <http://dx.doi.org/10.1016/j.msea.2009.01.022>.
- [5] Y.S. Li, N.R. Tao, K. Lu, Microstructural evolution and nanostructure formation in copper during dynamic plastic deformation at cryogenic temperatures, *Acta Mater.* 56 (2008) 230–241, <http://dx.doi.org/10.1016/j.actamat.2007.09.020>.
- [6] Y. Zhang, N.R. Tao, K. Lu, Mechanical properties and rolling behaviors of nano-grained copper with embedded nano-twin bundles, *Acta Mater.* 56 (2008) 2429–2440, <http://dx.doi.org/10.1016/j.actamat.2008.01.030>.
- [7] T. Konkova, S. Mironov, A.V. Korznikov, G. Korznikova, M.M. Myshlyayev, S. L. Semiatin, Grain structure evolution during cryogenic rolling of alpha brass, *J. Alloy. Compd.* 629 (2015) 140–147, <http://dx.doi.org/10.1016/j.jallcom.2014.12.241>.
- [8] T. Konkova, S. Mironov, A.V. Korznikov, G. Korznikova, M.M. Myshlyayev, S. L. Semiatin, An EBSD investigation of cryogenically-rolled Cu–30%Zn brass, *Mater. Character.* 101 (2015) 173–179, <http://dx.doi.org/10.1016/j.matchar.2015.02.004>.
- [9] B.B. Straumal, A.R. Kilmametov, Y. Kucheev, K.I. Kolesnikova, A. Korneva, P. Zieba, B. Baretzky, Transformation of Hume-Rothery phases under the action of high pressure torsion, *JETP Lett.* 100 (2014) 376–379, <http://dx.doi.org/10.1134/S0021364014181006>.
- [10] B.B. Straumal, A.R. Kilmametov, A.A. Mazilkin, L. Kurmanaeva, Y. Ivanisenko, A. Korneva, P. Zieba, B. Baretzky, Transformation of Cu(In) supersaturated solid solutions under high-pressure torsion, *Mater. Lett.* 138 (2015) 255–258, <http://dx.doi.org/10.1016/j.matlet.2014.10.009>.