

Recycling of Composites and Prepregs by Oxidative Catalysis

WP20-1491

Steve Nutt and Travis Williams
University of Southern California

25 Sept 2020




REPORT DOCUMENTATION PAGE					<i>Form Approved</i> OMB No. 0704-0188	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.						
1. REPORT DATE (DD-MM-YYYY) 05/09/2020		2. REPORT TYPE SERDP Project Outbrief			3. DATES COVERED (From - To) 8/27/2019 - 8/26/2021	
4. TITLE AND SUBTITLE Recycling of Composites and Prepregs by Oxidative Catalysis				5a. CONTRACT NUMBER 19-P-0094		
				5b. GRANT NUMBER		
				5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S) Steven Nutt Travis Williams				5d. PROJECT NUMBER WP20-1491		
				5e. TASK NUMBER		
				5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Southern California Department of Chemical Engineering and Materials Science 3651 Watt Way, VHE-406 Los Angeles, CA 90089-0241					8. PERFORMING ORGANIZATION REPORT NUMBER WP20-1491	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Strategic Environmental Research and Development Program 4800 Mark Center Drive, Suite 17D03 Alexandria, VA 22350-3605					10. SPONSOR/MONITOR'S ACRONYM(S) SERDP	
					11. SPONSOR/MONITOR'S REPORT NUMBER(S) WP20-1491	
12. DISTRIBUTION/AVAILABILITY STATEMENT DISTRIBUTION STATEMENT A. Approved for public release: distribution unlimited.						
13. SUPPLEMENTARY NOTES						
14. ABSTRACT The technical objectives of this project were to: demonstrate catalytic oxidation to disassemble epoxy composites; recover C fibers with retained architecture; demonstrate recovery of small molecules of value; and reduce hazmat waste from composite mfg.						
15. SUBJECT TERMS Recycling of Composites, Prepregs, Oxidative Catalysis						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 25	19a. NAME OF RESPONSIBLE PERSON Steven Nutt	
a. REPORT	b. ABSTRACT	c. THIS PAGE			19b. TELEPHONE NUMBER (Include area code)	
UNCLASS	UNCLASS	UNCLASS			213-740-1634	

Technical Objectives

Reduce hazmat waste
from composite mfg



Demonstrate recovery of
small molecules of value

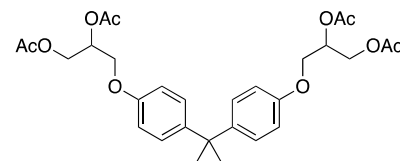


Recover C fibers with
retained architecture



Demonstrate catalytic
oxidation to disassemble
epoxy composites



Technical Approach

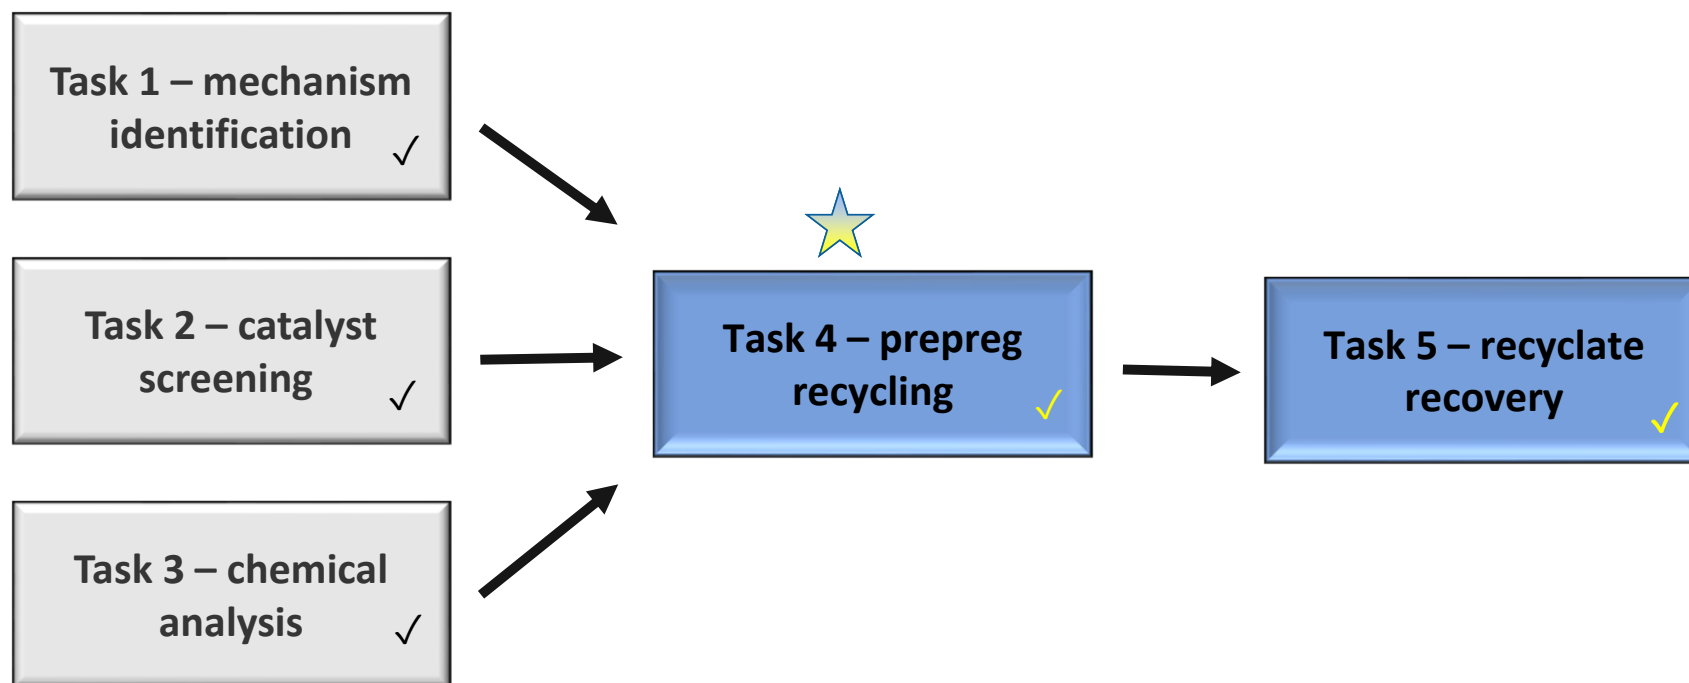

Project Team



Dr. Steve Nutt
PI, Advisor
M.C. Gill Composites
Center Director



Dr. Travis Williams
Co-PI, Advisor
USC Chemistry
Professor




Carlos Navarro
USC Ph.D.
Student,
Chemistry

Background

- Project initiated 2019
- NEED: Sustainable M&P for recycling/reuse of PMC's to reduce waste, exposure.



Background

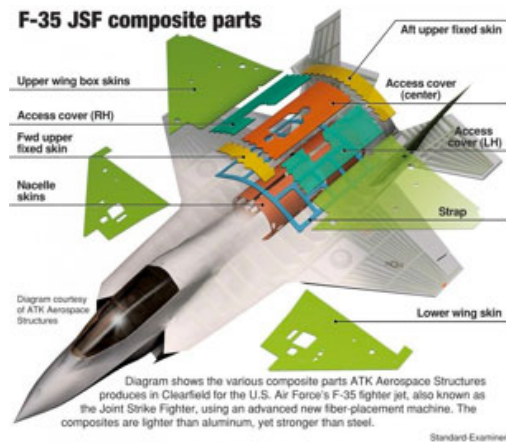

JSF composite parts

**Flexible
Body
Armour**



composite body armor



Tactical rocket motors




Autonomous Sea Hunter drone warship with CFRP hull




Panels and armor in ground vehicles

Results


- Describe results as they relate to the key tasks in your technical approach.

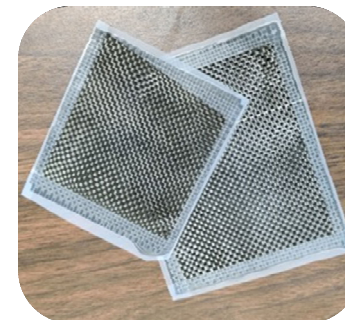


- Describe methods and techniques that were used and how they helped to accomplish the objective of the research.



- Reason to continue.

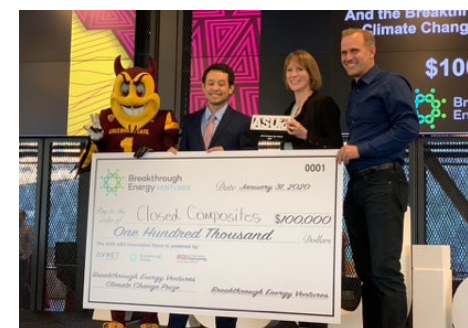

Mechanism identification – Task 1

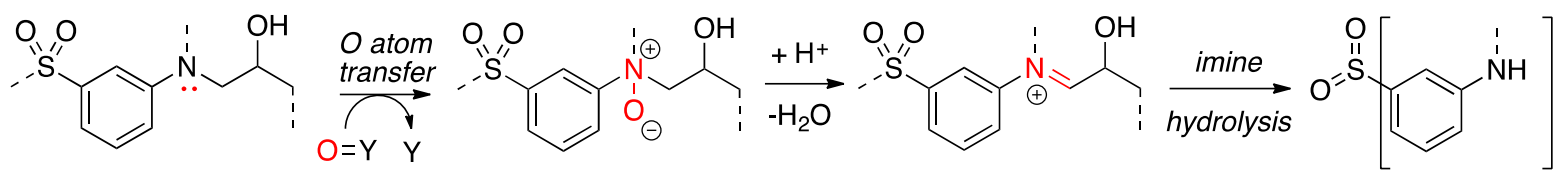


Can we move from H_2O_2 to
air with a catalyst?

Elimination

Polymer cleavage

Catalyst screening – Task 2

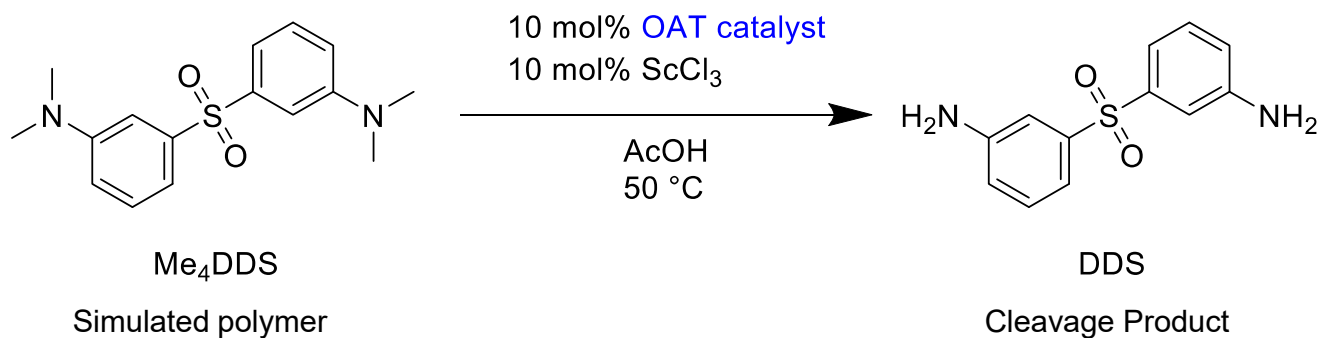

Metal	No ligand	1,10 - Phen	Salen
Fe(II)	Red	Red	White
Mn(II)	Blue	Green	Green
Ru(III)	Red	White	Red
Cu(I)	Blue	Green	Green
Co(II)	Red	Red	White


Green = consumed < 1 day

Blue = consumed in 2 days



Red = low / no reactivity

White = untested


Chemical analysis – Task 3

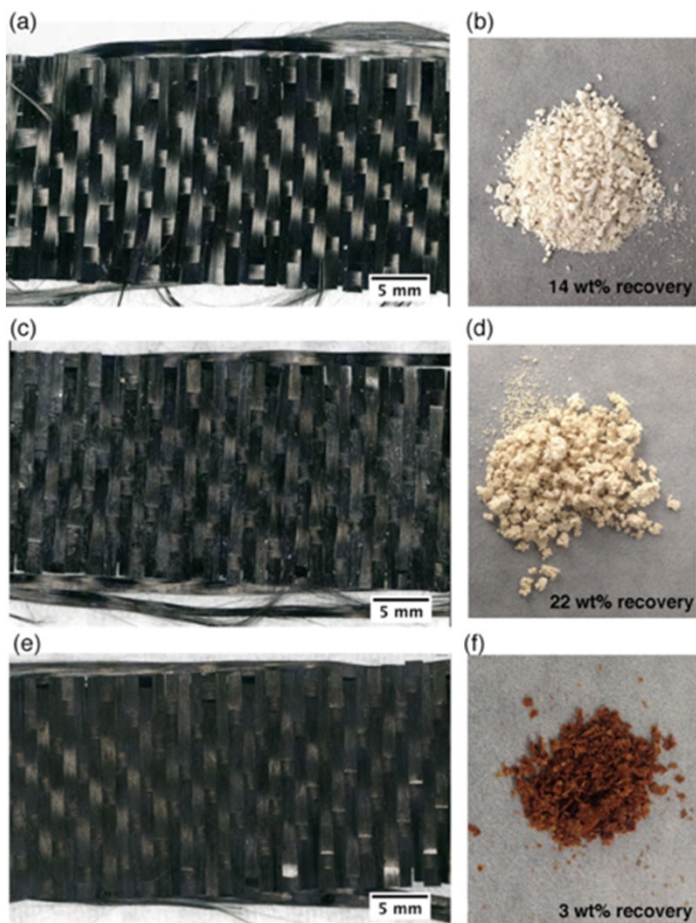

(mix of organic monomers)

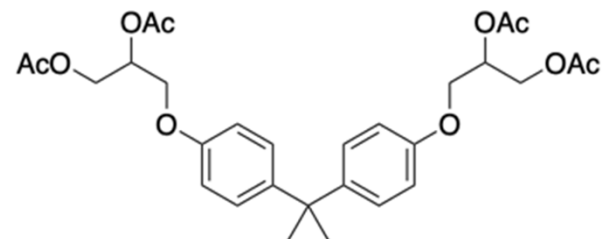
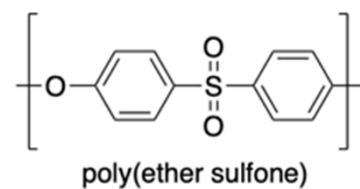


Prepreg recycling – Task 4

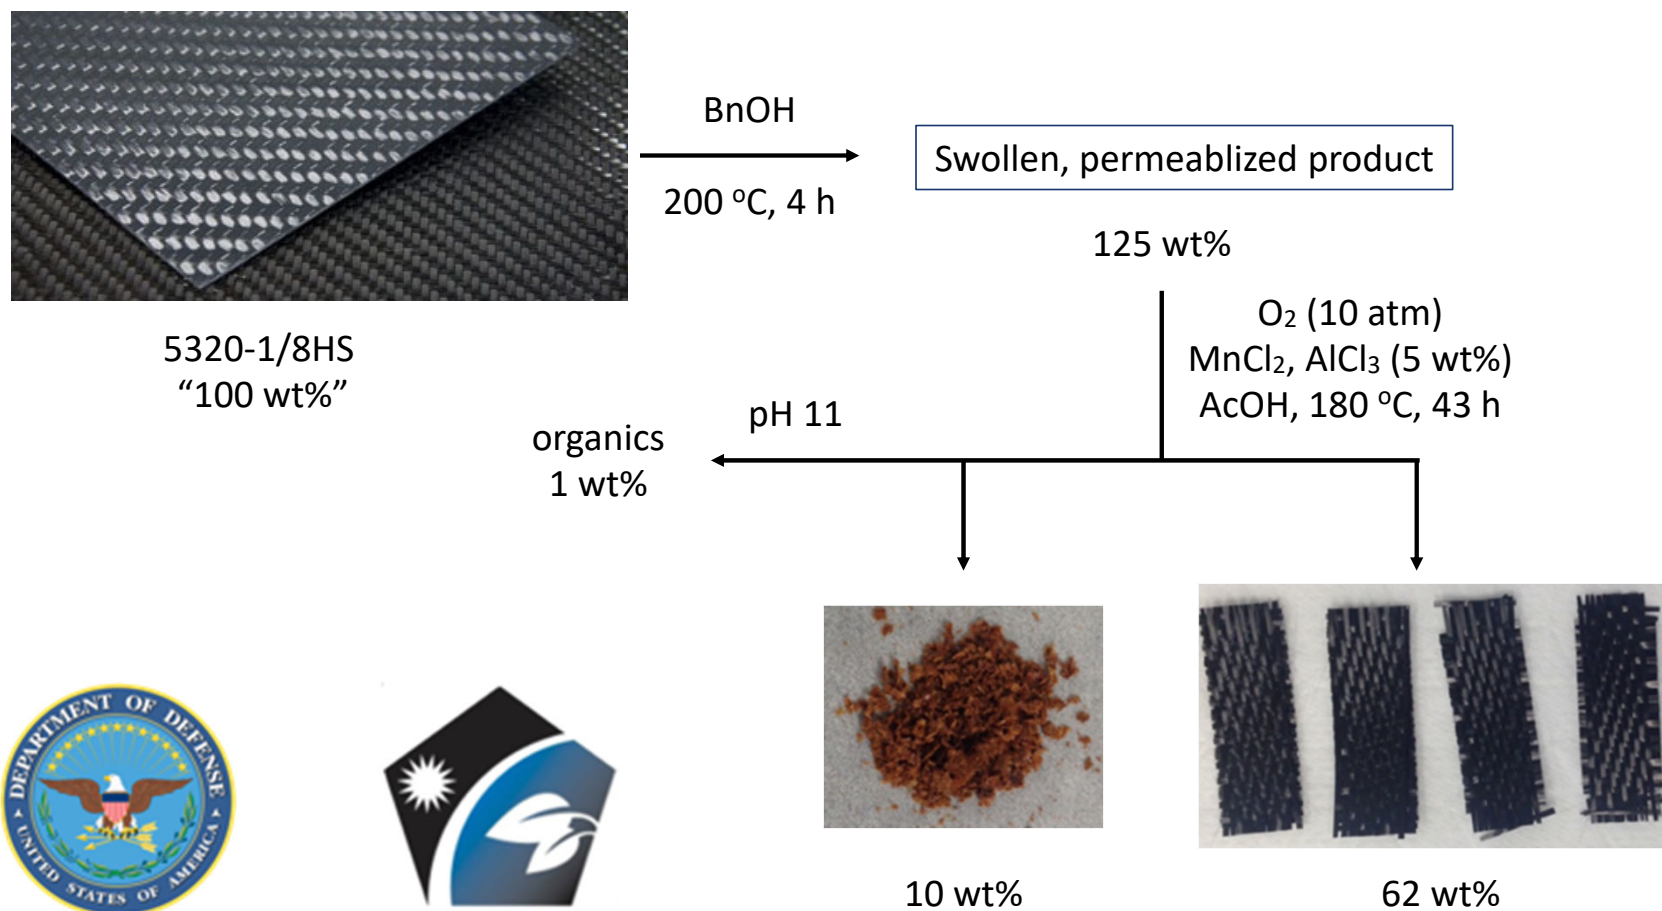

Recyclate recovery – Task 5

DDS by-products are accelerators for resin cure reaction

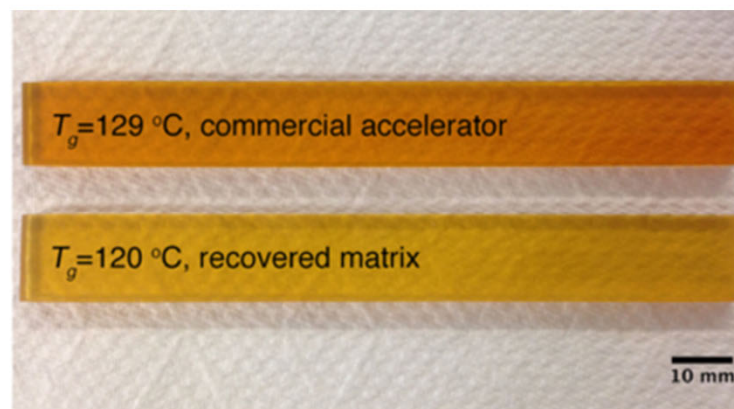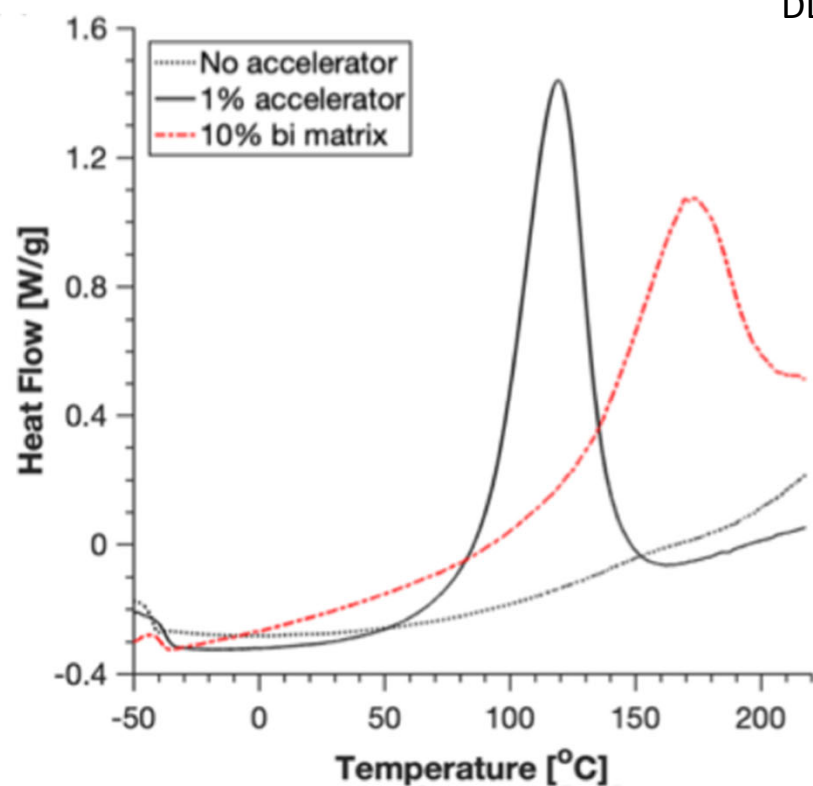

Next Steps

- Demonstrate property retention in recycled PMCs
- Scale up
- Accelerate

Technology Transfer

- Technology transfer is a critical and mandatory part of every SERDP project. The most successful technology transfer will include multiple types of approaches to reach multiple audiences.
- Consider the types of technology transfer that may be best suited to your project and provide a list of potential products/presentations as well as completed items. See examples on next slide.
- Target audiences should include EPA & State regulators, consultants, DoD Remedial Program Managers, and researchers.

Technology Transfer

- Startup formed - Closed Composites, LLC
- Funding awards



Wrigley competition



ASU competition

Startup – Closed Composites, LLC



Carlos Navarro
President
USC Ph.D.
Student,
Chemistry



Dr. Travis Williams
Board Secretary,
Advisor
USC Chemistry
Professor



Dr. Steve Nutt
Board Member,
Advisor
M.C. Gill Composites
Center Director

IP Landscape

- Lo, J.; Nutt, S. R.; Williams, T.J. “Recycling of Fiber Reinforced Polymers via Catalytic Oxidation” United States Provisional Patent 62/479,431, filed March 31, 2017.

Provisional was abandoned and claims were rolled in to US2018 16/234,062

- Ma, Y.; Navarro, C.; Nutt, S. R.; Williams, T. J. “Aerobic Depolymerization of Fiber-Reinforced Composites” United States Patent Application, US2018 16/234,062, filed December 27, 2018.




Non-provisional coverage of CFRP digestion

- Williams, T. J.; Nutt, S. R.; Ma, Y.; Navarro, C. A. “Recovery and Reuse of Acid Digested Amine/Epoxy-Based Composite Matrices” US Provisional Patent No. 62/902,158, filed September 18, 2019

Converting to PCT at VC request. Covers SERDP-sponsored inventions.

Key Points

- Take-aways
 - ◆ CF-epoxy parts are disassembled under moderate conditions
 - ◆ Fiber architecture and properties retained for reuse
 - ◆ Matrix components of value recovered for reuse
 - ◆ Scaling, accelerating, commercializing ahead

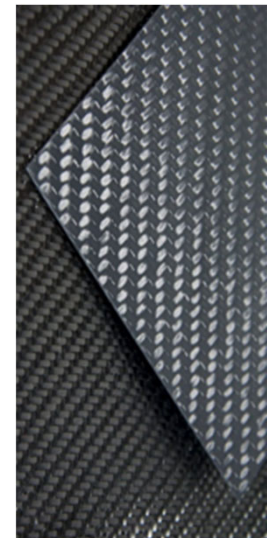

Future Research

- Tasks
 - ◆ Demonstrate depolymerization of cured CFRP from diverse sources
 - ◆ Scale up
 - ◆ Accelerate
 - ◆ Addressed mixed feedstocks
 - ◆ Develop routes for reuse (CFRP processing and properties, fiber surface treatments, tougheners)
- Rough cost estimate for follow-on research: \$700K/yr for 3 yrs

BACKUP SLIDES

Publications

Materials Horizons



FOCUS

View Article Online
View Journal



Cite this: DOI: 10.1039/d0mh01085e

A structural chemistry look at composites recycling

Carlos A. Navarro,^a Cassandra R. Giffin,^a Boyang Zhang,^a Zehan Yu,^b Steven R. Nutt^b and Travis J. Williams^{a*}

Composite materials, especially carbon fiber-reinforced polymers (CFRPs), are high-performance class of structural materials now commonly used in aircraft, marine, and other applications, with emerging large-scale use in the automotive and civil engineering applications. The difficulty of recycling these materials is a key obstacle preventing their further application in larger markets. For decades, the engineering community has pursued physical methods to recover value from end-of-life composite waste. This work has generated scalable methods to recover modest value from CFRP waste, but because of their low value recovery, these are applied to a small fraction of CFRP waste. By contrast, relatively few methods to recycle CFRPs have been based on strategic approaches systematically to deconstruct the thermoset polymers that hold them together. In this Focus Article, we will show the emergence of these structure-focused approaches to CFRP recycling and illustrate the path of this research toward the ultimate realization of methods to recover both the reinforcing fibers and the thermoset materials that comprise modern CFRPs.

Received 3rd July 2020.
Accepted 21st August 2020
DOI: 10.1039/d0mh01085e

rsc.li/materials-horizons

Introduction

Fiber-reinforced polymer (FRP) composites are structural materials that offer superior specific properties (strength and modulus), longer life, and increased efficiency compared to conventional structural metals.¹ FRPs are now commonly used in aerospace, wind turbine, marine, and sporting goods applications, with emerging large-scale use in the automotive industry and some civil engineering applications. Most of the

parts by weight, FRPs are also important in the wind energy industry: glass fiber-reinforced polymers are currently the primary structural material in wind turbine blades. The wind industry is motivated to transition to carbon fiber for manufacturing larger turbines. With blade lengths now exceeding 100 m, carbon fiber is used selectively in spar caps to provide the stiffness required to prevent column collisions under gust loads. Composites are also widely seen in high performance sporting goods: modern marine vessels to racing bicycles, golf shafts

"A Structural Chemistry Look at Composites Recycling" CA Navarro, CR Giffin, B Zhang, Z Yu, SR Nutt, TJ Williams, *Materials Horizons* Aug (2020) DOI


Polymer Degradation and Stability 175 (2020) 109125



Contents lists available at ScienceDirect

Polymer Degradation and Stability

journal homepage: www.elsevier.com/locate/polydegstab



Recovery and reuse of acid digested amine/epoxy-based composite matrices

Yijia Ma^{a,*}, Carlos A. Navarro^b, Travis J. Williams^b, Steven R. Nutt^a

^a Department of Chemical Engineering and Materials Science, University of Southern California, USA
^b Loker Hydrocarbon Research Institute and Department of Chemistry, University of Southern California, USA

ARTICLE INFO

Article history:
Received 17 June 2019
Received in revised form
27 February 2020
Accepted 1 March 2020
Available online 4 March 2020

Keywords:
Recycling
Reuse
Acid digestion
Composites
Epoxy
Resin formulation

ABSTRACT

Chemical recycling of thermoset composites has been focused largely on recovering high-value carbon fibers with property retention, while recovery and reuse of decomposed polymer matrix residues is generally overlooked, despite the fact that matrix recycling constitutes an essential component of a sustainable approach to the overall problem. Our previous study demonstrated that oxidative acid digestion can be deployed effectively to recover near-virgin quality carbon fibers from amine-cured epoxy composites. In the present study, we investigate the viability of recovery and reuse of the decomposed amine/epoxy residue after acid digestion of the matrix, effectively closing the recycling loop. We find that polymer matrix residues recovered from acid digestion solutions via neutralization and precipitation contain molecular components of the epoxies in which aromatic regions are preserved. The recovered matrix residues are blended into virgin resin formulations and two approaches are evaluated for potential reuse. Approach I utilizes the matrix residue as an accelerator for a virgin anhydride/epoxy formulation that contains no accelerator and thus cannot be self-catalyzed. We discover that adding matrix residue produces catalytic effects on the curing reaction. In general, anhydride/epoxy samples blended and cured with recovered matrix residues are homogenous and exhibit thermal and mechanical properties comparable to specimens cured with a commercial accelerator. Approach II deployed the matrix residue as a filler for virgin anhydride-based epoxies with a commercial accelerator to produce blended formulations. In such cases, blended formulations yielded acceptable retention of thermal and mechanical properties, provided the fraction of matrix residue added did not exceed 10 wt%.

© 2020 Elsevier Ltd. All rights reserved.

"Recovery and reuse of acid-digested amine/epoxy composite matrices" Y Ma, CA Navarro, TJ Williams, SR Nutt, *Polymer Degradation & Stability* 175 (2020) 109125 DOI

Project Funding

	FY20
Funds received to date (\$K)	\$200K
% Expended	100%
Funds Remaining (\$K)	-

Technology Transfer Examples

- Presentations at key conferences
- Web-based tools (see example at link)
 - ◆ <http://t2.serdp-estcp.org/>
- Technology fact sheets
- SAMPE LA chapter open house

Supporting Material

- Provide any appropriate supporting material that could not be included in the brief, if necessary