


AD A013502

INVESTIGATION OF RHEOLOGICAL
PROPERTIES OF DILUTE SOLUTIONS
OF POLYMERIC ANTIMIST AGENTS
IN HYDROCARBON FUELS

Interim Report
AFLRL No. 59

by

R. J. Mannheimer
W. D. Weatherford, Jr.

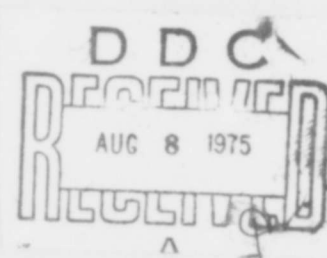

Approved for public release; distribution unlimited

Prepared by

U. S. Army Fuels and Lubricants Research Laboratory
Southwest Research Institute
San Antonio, Texas

Under contract to

U. S. Army Mobility Equipment Research and Development Center
Petroleum and Materials Department
Fort Belvoir, Virginia

Contract No. DAAK02-73-C-0221

June 1975

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Trade names cited in this report do not constitute an official endorsement or approval of the use of such commercial hardware or software.

DDC Availability Notice

Qualified requestors may obtain copies of this report from Defense Documentation Center, Cameron Station, Alexandria, Virginia 22314.

Disposition instructions

Destroy this report when no longer needed. Do not return it to the originator.

UNCLASSIFIED

12

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER AFLRL No. 59 ✓	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Investigation of Rheological Properties of Dilute Solutions of Polymeric Antimist Agents in Hydrocarbon Fuels	5. TYPE OF REPORT & PERIOD COVERED Interim Report	6. PERFORMING ORG. REPORT NUMBER AFLRL 59
7. AUTHOR(s) R.J. Mannheimer W.D. Weatherford, Jr.	8. CONTRACT OR GRANT NUMBER(s) DAAK02-73-C-0221	9. PROGRAM ELEMENT PROJ. TASK AREA & WORK UNIT NUMBERS 19P.
10. PERFORMING ORGANIZATION NAME AND ADDRESS U.S. Army Fuels and Lubricants Research Laboratory P.O. Drawer 28510 San Antonio, Texas 78284	11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army Mobility Equipment R&D Center Petroleum and Materials Department Fort Belvoir, Virginia	12. REPORT DATE Jun 1975
13. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	14. SECURITY CLASS. (of this report) Unclassified	15. NUMBER OF PAGES
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited	17. SECURITY CLASS. (of this report)	18. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)	DDC RECEIVED AUG 8 1975 A	
18. SUPPLEMENTARY NOTES	19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Rheology, viscoelasticity, polymer solutions, elongational viscosity, porous media, antimist.	
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A dilute solution of polymeric antimist additive is found to offer unusually high resistance to flow through metal filters. This apparent anomaly is not due to filter plugging or polymer adsorption but may be explained in terms of an elongational viscosity that cannot be observed in ordinary viscometric flow. Measurements in different size filters indicate a slightly higher resistance with finer pore sizes; however, end effects were not significant. Preliminary results indicate that this anomalous resistance may be related to antimisting effectiveness.		

387339

DN

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

[A large rectangular box containing a faint, mostly illegible document with some faint lines and markings.]

ADDRESS TO BE	
BY	XXXXXX
FOR	SECRET
DEPARTMENT	
ACTIVITY	
ST	
ADMINISTRATIVE SECURITY CODE	
FILE NO.	
DATE	
A	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

FOREWORD

This report was prepared at the U.S. Army Fuels and Lubricants Research Laboratory, Southwest Research Institute, under DOD Contract No. DAAK02-73-C-0221. The project was administered by the Fuels, Lubricants, and Coatings Division, Petroleum and Materials Department, U. S. Army Mobility Equipment Research and Development Center, Fort Belvoir, Virginia, with Mr. F. W. Schaeckel serving as Project Monitor. The AFLRL project has been conducted under the consecutive cognizance of Dr. James Bryant and Major R. Stryjewski, U. S. Army Deputy Chief of Staff, Research and Development and Acquisition.

Acknowledgement is given to Mr. R. A. Nava, who conducted the experiments described in this report and to Mr. J. P. Pierce who prepared the polymer solutions. Special acknowledgement is given to Messrs. H. L. Ammlung, F. W. Schaeckel, R. D. Quillian, J. T. Gray, and B. R. Wright for their encouragement, comments, assistance, and suggestions.

TABLE OF CONTENTS

	<u>Page</u>
LIST OF ILLUSTRATIONS	<i>vi</i>
LIST OF TABLES	<i>vi</i>
INTRODUCTION	1
OBJECTIVES	2
APPROACH	2
EXPERIMENTAL	4
Description of Apparatus and Procedure	4
Physical Properties of Porous Media	6
Preparation and Properties of Blends of Antimist Agent in JP-8 Fuel	6
Discussion of Results	7
SUMMARY AND CONCLUSIONS	12
REFERENCES	12

PRECEDING PAGE BLANK NOT FILMED

LIST OF ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	Microrheology of Flexible Polymer Molecule in Dilute Solution	2
2	Diagram of Apparatus and Filter Holder	5
3	Flow Characteristics of a 0.2-Percent AM-1 Solution in Two Different Grade Filters	7
4	Flow Characteristics of a 0.2-Percent AM-1 Solution in two Different Grade Filters	8
5	Use of Consistency Parameters for Flow Data in Different Filters	9
6	Effect of AM-1 Content on Relative Fluidity and Relative Flashback	11

LIST OF TABLES

<u>Table</u>		<u>Page</u>
1	Physical Properties of Sintered Bronze Filters	6
2	Viscosity for Neat and Antimist JP-8 Fuel Blends	7
3	Flow Properties of a 0.2-Percent AM-1 Solution in Different Filters	10
4	Power Law Parameters for two 0.2-Percent AM-1 Solutions Having the Same Shear Viscosity and Gum Content	10

INTRODUCTION

This report on the rheological properties of dilute polymer solutions constitutes a small part of a larger program currently under investigation by the U.S. Army Fuels and Lubricants Research Laboratory (AFLRL) to determine the fire safety and physical properties of fuels containing polymeric antimist additives. An overview of the results obtained by this laboratory and various U.S. organizations has been presented at the 45th meeting of the AGARD/NATO Propulsion and Energetics Panel on Aircraft Fire Safety in Rome, Italy, 7-11 April, 1975.^{(1)*}

One of the most important properties of a liquid that determines its relative resistance to atomization is the viscosity. Even with most non-Newtonian liquids there is usually a good correlation between the stability of a liquid jet and the apparent viscosity, provided that it is measured at the appropriate rate of shear and provided that the fluid is essentially inelastic.⁽²⁾ On the other hand, viscoelastic liquids such as dilute polymer solutions may have very low viscosities and still be highly resistant to atomization! This phenomenon is even more perplexing in light of stability analyses that predict that jets of viscoelastic liquids will be less stable than purely viscous liquids! Some recent studies of jet breakup have verified that, with dilute polymer solutions, the initial instability of the jet occurred sooner than would be expected for a purely viscous liquid (as is predicted by theory); however, the ensuing breakup proceeds by an altogether different mechanism.⁽³⁾ Specifically, the breakup of a viscous jet is characterized by the exponential growth of surface waves and, consequently, is rather abrupt. On the other hand, the breakup of a viscoelastic liquid is much more gradual and is characterized by the formation of a series of droplets held together by thin threads much like a string of beads. The important point is that the formation of a thin thread from a larger jet is associated with an elongational or stretching flow rather than the more familiar shear flow. Furthermore, it has been predicted that viscoelastic fluids should exhibit a much higher resistance when stretched than when sheared. For example, in the model of a rubber-like liquid, the viscosity is independent of the shear rate, i.e., it would appear to be Newtonian from shear experiments, but is an increasing function of the rate of elongation.⁽⁴⁾

Some physical insight as to the mechanism for this behavior can be provided by the micro-rheology of a dilute polymer solution. It is generally accepted that a typical linear polymer exists in a dilute solution in the form of a highly flexible coil⁽⁵⁾ (Figure 1a). If a fluid element of this solution is subjected to a simple shearing flow, as is produced in a typical viscometer, the primary response of the polymer to the impressed velocity gradient is a clockwise rotation. At low rates of shear and with a low viscosity liquid such as JP-8, the solvent will offer very little resistance to this rotational motion; consequently, the polymer molecule will remain in a relatively undeformed state and the viscosity of the solution will be low and essentially independent of the shear rate. An altogether different situation arises if a filament of fluid is subjected to a simple elongation (Figure 1b). In this case, the hydrodynamic forces are much more efficient in being able to orient and deform the polymer molecule.⁽⁶⁾ Thus, the elongational flow is resisted primarily by the mechanical properties of the polymer, while the shear flow is resisted primarily by the mechanical properties of the solvent.

While several rheological models predict that a viscoelastic liquid can exhibit a much higher resistance to elongation than to shear, experimental verification of these predictions has been conspicuously absent due to the difficulty of producing a rapid elongational flow; however, recently it has been shown that an elongation flow field can be produced by utilizing a porous bed.⁽⁷⁾ While this geometry is too complex for precise analysis, an approximate analysis has shown that the

*Superscript numbers in parentheses refer to references at the end of the report.

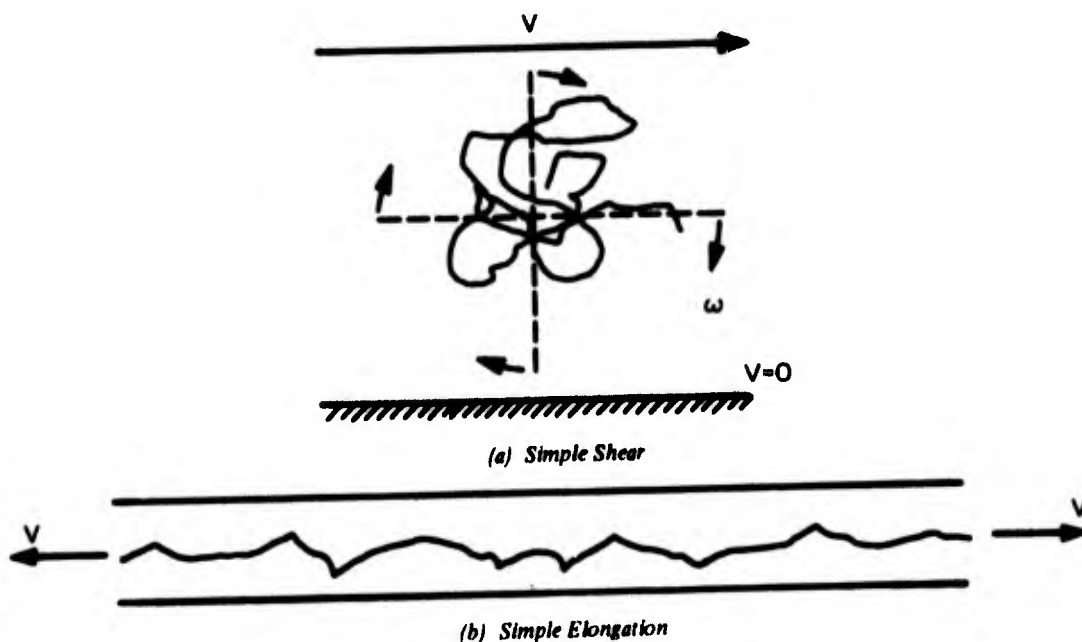


FIGURE 1. MICRORHEOLOGY OF FLEXIBLE POLYMER MOLECULE IN DILUTE SOLUTION

primary mode of deformation will be elongation when the length-to-width ratio of the pore is close to unity. This would be the case for a porous bed made of uniform spheres. On the other hand, the primary mode of deformation will be shear when the length-to-width ratio of the pore approaches infinity, e.g., a porous bed formed by a bundle of capillary tubes. Experimental flow measurements through porous media have confirmed that viscoelastic liquids require much higher pressure drops (sometime two orders of magnitude higher) than a purely viscous liquid of equivalent viscosity.⁽⁷⁾

OBJECTIVES

The primary objectives of this investigation are as follows:

- (1) Establish that dilute solutions of polymer antimist agents in JP-8 exhibit an abnormally high resistance to steady flow through porous media that is in no way due to adsorption or filtration of the additive,
- (2) Determine the effects of physical properties of the porous media such as particle size and permeability on the relative resistance of these solutions,
- (3) Determine if the resistance to flow in porous media can be related to antimist effectiveness.

APPROACH

It has been shown that the anomalous behavior of viscoelastic liquids in porous media can be predicted by the Deborah Number⁽⁵⁾ (defined as the ratio of the characteristic fluid relaxation time to the characteristic time scale of the deformation process). Unfortunately, the normal stress

differences that are required to calculate the fluid relaxation time are difficult to measure for low viscosity solutions; consequently, we will take a less basic approach.

At low Reynolds' numbers*, the flow of Newtonian liquids through a porous bed is governed by the Darcy equation:

$$Q = \frac{KA\Delta P}{\mu L} \quad (1)$$

where Q is the volumetric flow rate, A is the cross-sectional area of the bed, L is the length of the bed, K is the permeability, ΔP is the pressure drop, and μ is the viscosity. Since dilute solutions (0.2 percent) of AM-1† in JP-8‡ appears to be Newtonian in steady flow through capillary tubes, deviations from Equation 1 can be used to detect viscoelastic behavior, provided it can be established that adsorption or filtration effects are not significant. This can be accomplished by measuring the permeability of the porous media with Newtonian (inelastic) liquids of known viscosity (i.e., mineral oil and JP-8) before and after the use of the polymer solutions and also by showing that the flow of these solutions does not exhibit any time dependency or hysteresis effects.

In order to investigate the effect of pore size and permeability on the relative resistance of viscoelastic liquids, we will assume that the porous bed can be approximated by a bundle of capillary tubes.⁽⁸⁾ While it is realized that this oversimplified model neglects the pore entrance effects that are probably the primary reason for the anomalous behavior of viscoelastic liquids, it might at least be able to serve as a basis for comparing porous beds consisting of similarly shaped particles. Using this approach, we can define consistency variables:

$$\tau_e = \frac{2D_p \epsilon \Delta P}{25(1 - \epsilon)L} \quad (2)$$

$$F(\tau_e) = \frac{3(1 - \epsilon)Q}{AD_p \epsilon^2} = \frac{1}{\tau_e^3} \int_0^{\tau_e} \tau^2 f(\tau) d\tau \quad (3)$$

Where τ_e is an average shear stress scaled to the porous media and $4F(\tau_e)$ is an average shear rate. Accordingly, a "Darcy Viscosity" can be defined as:

$$\eta_e = \frac{\tau_e}{4F(\tau_e)} \quad (4)$$

When η_e is Newtonian, Equation 4 reduces to the Darcy Equation in which

$$K = \frac{D_p^2 \epsilon^3}{150(1 - \epsilon)^2} \quad (5)$$

is the predicted permeability. In the following experiments we will measure the permeability and particle size and then use Equation 5 to calculate the porosity. If the analog to capillary tube

* $NR_e = \frac{D_p Q \rho}{150\mu(1 - \epsilon)A} < 0.05$, ρ is the density, ϵ is the porosity, and D_p is the particle diameter.

† Rheological studies have initially been confined to an antimist agent designated by AFRL as AM-1. This is a proprietary product of Continental Oil Co.; hence, little can be said about its chemical constitution except that it is a long-chain hydrocarbon polymer with a molecular weight in excess of one million.

‡ Tentative Military Specification (equivalent to Jet A-1).

experiments is correct, flow data of viscoelastic solutions in different porous media should result in the same Darcy Viscosities when expressed in terms of τ_e and $F(\tau_e)$.

A second and equivalent approach is to assume a rheological model for the fluid and then to calculate the flow curve. Since the behavior of viscoelastic solutions in porous media is similar to that of a shear thickening fluid (it is important to note that this is just an apparent effect) one could express such behavior in terms of a power law model, i.e.,

$$\tau = mf(\dot{\tau})^n \quad (6)$$

Where τ is the shear stress, $f(\dot{\tau})$ is the shear rate, and m and n are rheological parameters. Using Equation 6 with Equations 2 and 3, the predicted pressure drop for the flow of a power law fluid becomes⁽⁸⁾:

$$\frac{\Delta P}{L} = \frac{150m \left(9 + \frac{3}{n}\right)^n (1 - \epsilon)^{n+1} Q^n}{12D_p^{n+1} \epsilon^{2n+1} A^n} \quad (7)$$

The rheological parameters m and n will be obtained by curve fitting the experimental data with Equation 7.

The equivalence of the two approaches is readily apparent by the fact that we can also define a Darcy Viscosity from the Power Law Parameters:

$$\eta_e = m^{1/n} \tau_e^{1 - (1/n)} \quad (8)$$


Both methods have their advantages and disadvantages. For example, analysis of flow data by consistency variables is simple and direct, and the resulting Darcy Viscosity is measured in familiar units of poise; however, it is generally a complex function of the shear stress or shear rate. On the other hand, while the Power Law Parameters are slightly more difficult to obtain and have less physical meaning to us, they are able to correlate the flow over a wide range of conditions, thereby making it easier to quantitatively compare two experiments. Since the rheological behavior in capillary tubes indicate that the dilute AM-1 solutions are Newtonian, Equation 7 will not be able to predict viscoelastic behavior; however, it may be possible to determine m and n in a particular porous bed and then predict the flow in a bed of similar pore geometry but different pore size and permeability.

In order to determine whether the resistance of AM-1 solutions is related to fire safety, we will compare the effect of AM-1 on the mist flammability and the Darcy Viscosity. The mist flammability will be determined by the Mist Flashback Test⁽⁹⁾, which has been used to simulate the air shear encountered in a full-scale helicopter crash.


EXPERIMENTAL

Description of Apparatus and Procedure

Flow data were obtained with the simple apparatus illustrated in Figure 2a. This device is essentially a scaled-down version of the capillary tube viscometer used in the rheological studies of

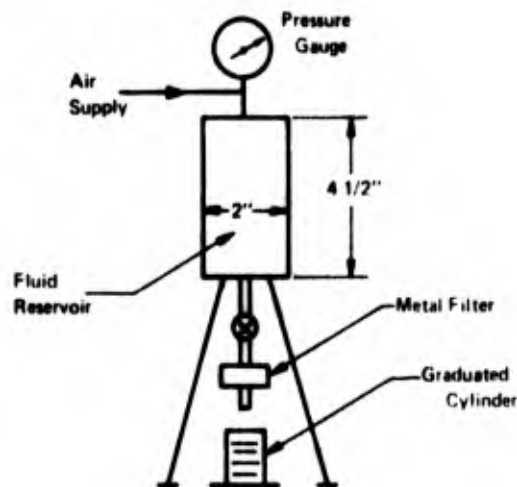

(a) Diagram of Apparatus

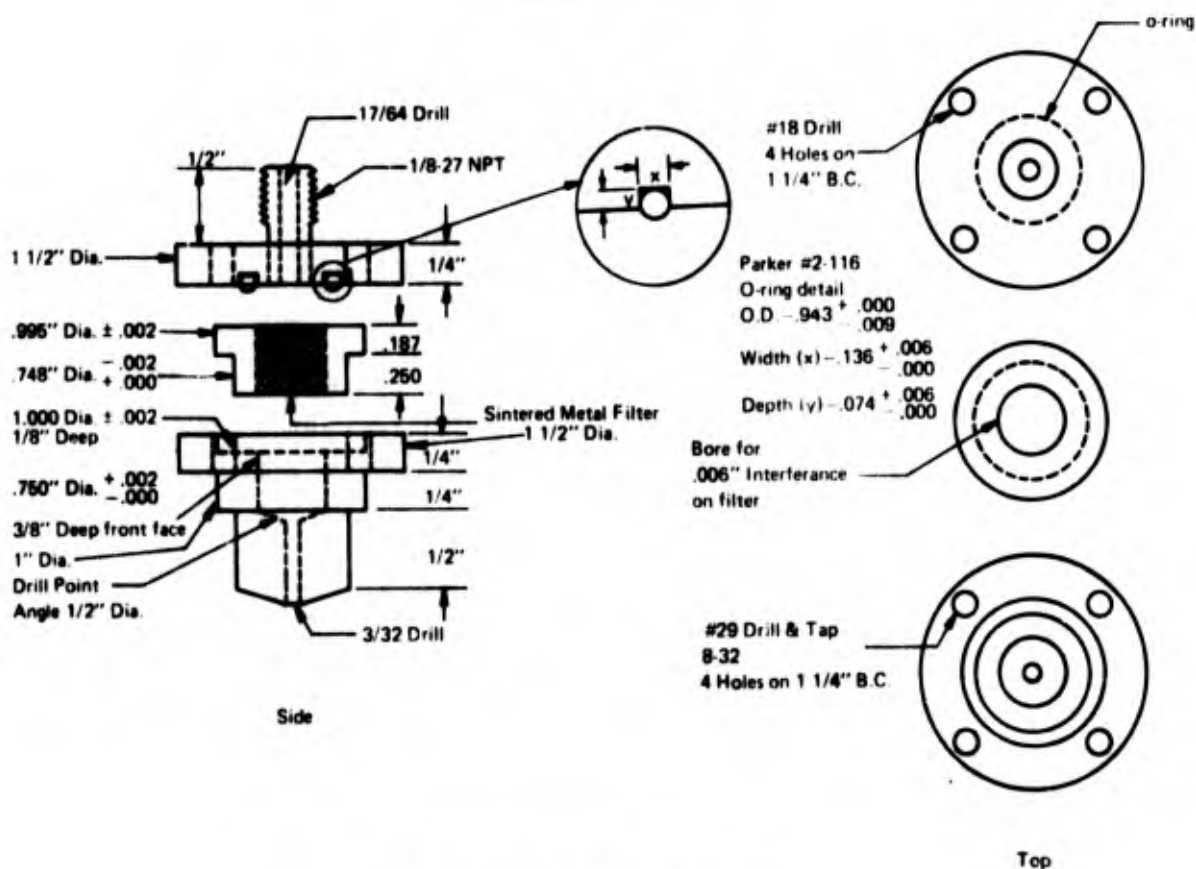

(b) Detail Drawing of Filter Holder

FIGURE 2. DIAGRAM OF APPARATUS AND FILTER HOLDER

emulsified fuels⁽¹⁰⁾ in which the capillary tube has been replaced by a metal filter (details of the filter holder assembly are shown in Figure 2b). In a typical experiment, one would set the pressure and then measure the mass or volumetric flow rate by collecting a sample over a particular time interval. It was found that determining the weight of mineral oil was more accurate than determining its volume; however, with low viscosity liquids, both methods worked equally well.

Measurements were made at both increasing and decreasing pressures and over different time intervals so as to detect changes in permeability due to adsorption or filtration effects.

Physical Properties of Porous Media

The porous media used in this investigation were in the form of sintered bronze filters.* Two different grades (460 and 230) corresponding to two different particle sizes, and two different filter sizes (1/8 X 5/8 in. and 7/16 X 7/16 in.) were used in the investigation. Eight of the 1/8-in. filters were pressed into a single holder to form a composite filter having a thickness of approximately 1 inch. With the 7/16-in. filters, only a single element was used.

The dimensions of the metal particles in the 460- and 230-grade filters were determined with a microscope and calibrated eyepiece. Each particle was characterized by two length dimensions x_1 and x_2 . The mean and standard deviation of these measurements are presented in Table 1. The ratios of these average dimensions were 0.78 and 0.81 for the 460 and 230 grades, respectively. These ratios show that the particles are not truly spherical, but that both grades have essentially the same characteristic shape. An average particle diameter was calculated by taking the arithmetic average of the two length dimensions, and was found to be 0.038 cm and 0.076 cm for the 460 and 230 grades, respectively.

TABLE 1. PHYSICAL PROPERTIES OF SINTERED BRONZE FILTERS

Grade	Particle Dimensions				X_1/X_2	D_p (cm)	Filter Dimensions		Permeability (Darcies)	Porosity*
	Mean X_1 (cm)	Std. Dev. σ_1 (cm)	Mean X_2 (cm)	Std. Dev. σ_2 (cm)			Length (cm)	Area (cm ²)		
460	0.0328	0.003	0.0422	0.003	0.78	0.038	1.11	1.0	70 to 89	0.324 to 0.342
230	0.0670	0.004	0.0840	0.005	0.81	0.076	1.13	1.0	310 to 322	0.323 to 0.332
460	—	—	—	—	—	—	2.51†	1.92	85	0.330
230	—	—	—	—	—	—	2.57†	1.92	300	0.323

*Calculated from Equation 5.

†Eight 1/8-in. elements.

Permeabilities were determined from the slope of the flow curves for both mineral oil (133 cp at 78°F) and a JP-8/mineral oil blend (8.0 cp at 78°F). Five different single-filter elements exhibited a range in permeabilities of 72 to 89 Darcies for the 460 grade and 310 to 322 Darcies for the 230 grade. The two composite filters were very close to these values.

Preparation and Properties of Blends of Antimist Agent in JP-8 Fuel

The antimist agent, AM-1, is normally received as a 5-percent concentrate (approximately) in low-volatility kerosene. Laboratory batches (less than 5 gallons) of dilute solutions of this additive are routinely prepared by adding a predetermined volume of the concentrate to a measured volume of base fuel with continuous stirring, using a small propeller-type blade. The solution is stirred at a slow rate until it becomes clear and free of undissolved aggregates of concentrate. Stirring is continued for about one hour after dissolution appears to be complete.

*Perth Metal Industries, Ltd., P.O. Box 572, Monteith Avenue, Stratford, Ontario.

Following preparation of a new batch of AM-1 anti-mist fuel, the concentration of polymeric antimist agent is routinely checked by measuring the existent gum content (ASTM D-381) of the blend and of its base fuel. In addition, the flash point (Penske-Martens, D-93) is determined to confirm that the blending procedure has not caused significant evaporation losses. Since capillary tube data of AM-1 solutions produced linear graphs up to wall shear rates of 1300 sec^{-1} and concentrations up to 0.2 percent, the simpler ASTM D-445 viscosity method was used routinely to check the viscosity of each newly prepared blend. The data presented in Table 2 illustrate the influence of additive content on viscosity (ASTM D-445) for several different concentrations of AM-1 in JP-8R.

TABLE 2. VISCOSITY FOR NEAT AND ANTI-MIST JP-8 FUEL BLENDS

AM-1 Content (wt%)	Viscosity [μ S (ASTM D-445) @ 24°C]
0.0	2.1
0.05 AM-1	3.0
0.07 AM-1	3.3
0.1 AM-1	3.9
0.2 AM-1	6.5
0.3 AM-1	9.0

Discussion of Results

Flow data for triplicate experiments with a 0.2-percent AM-1 solution through two different grade (460 and 230) filters are presented in Figure 3. Since the dashed lines are the expected results

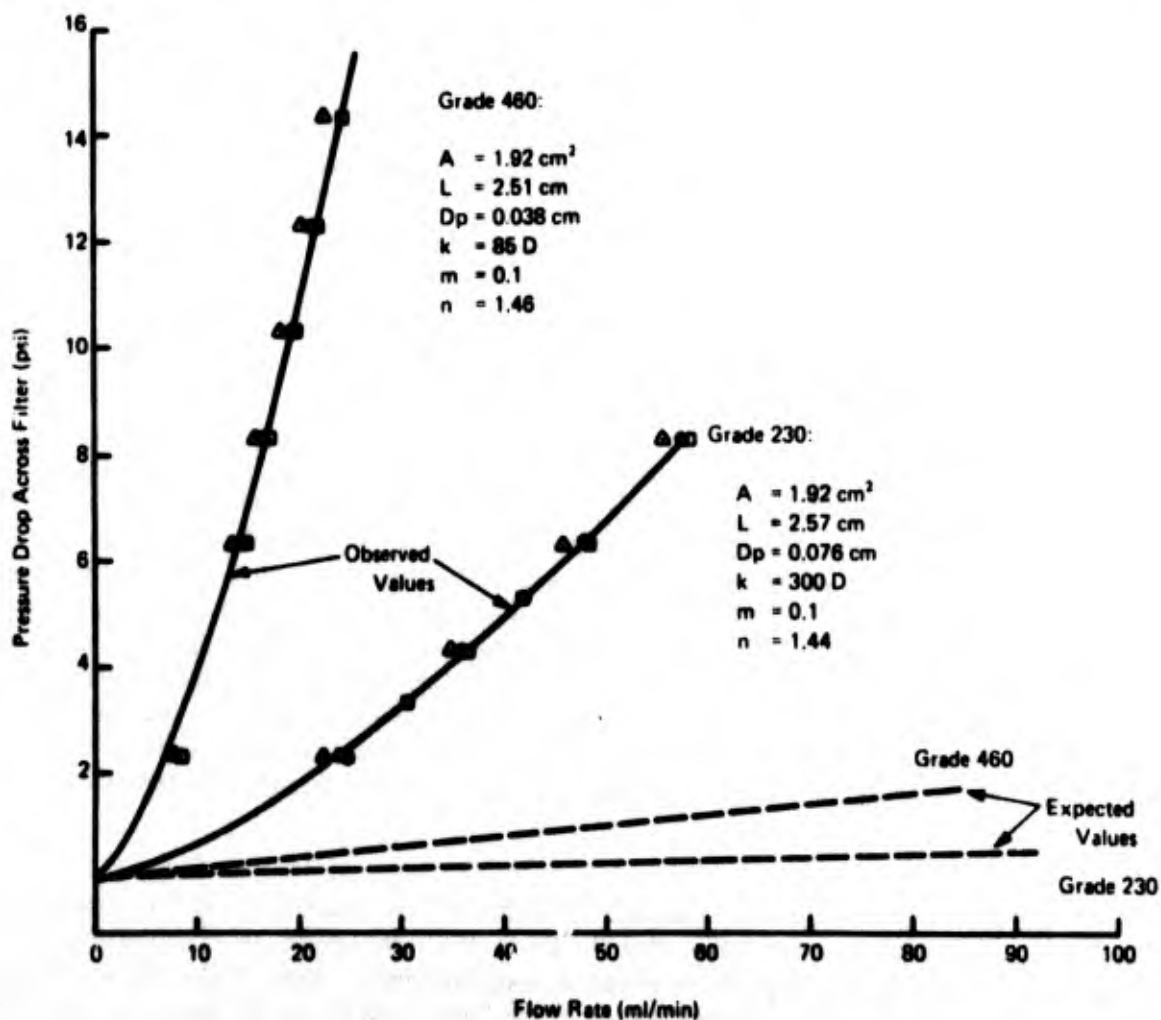


FIGURE 3. FLOW CHARACTERISTICS OF A 0.2-PERCENT AM-1 SOLUTION IN TWO DIFFERENT GRADE FILTERS

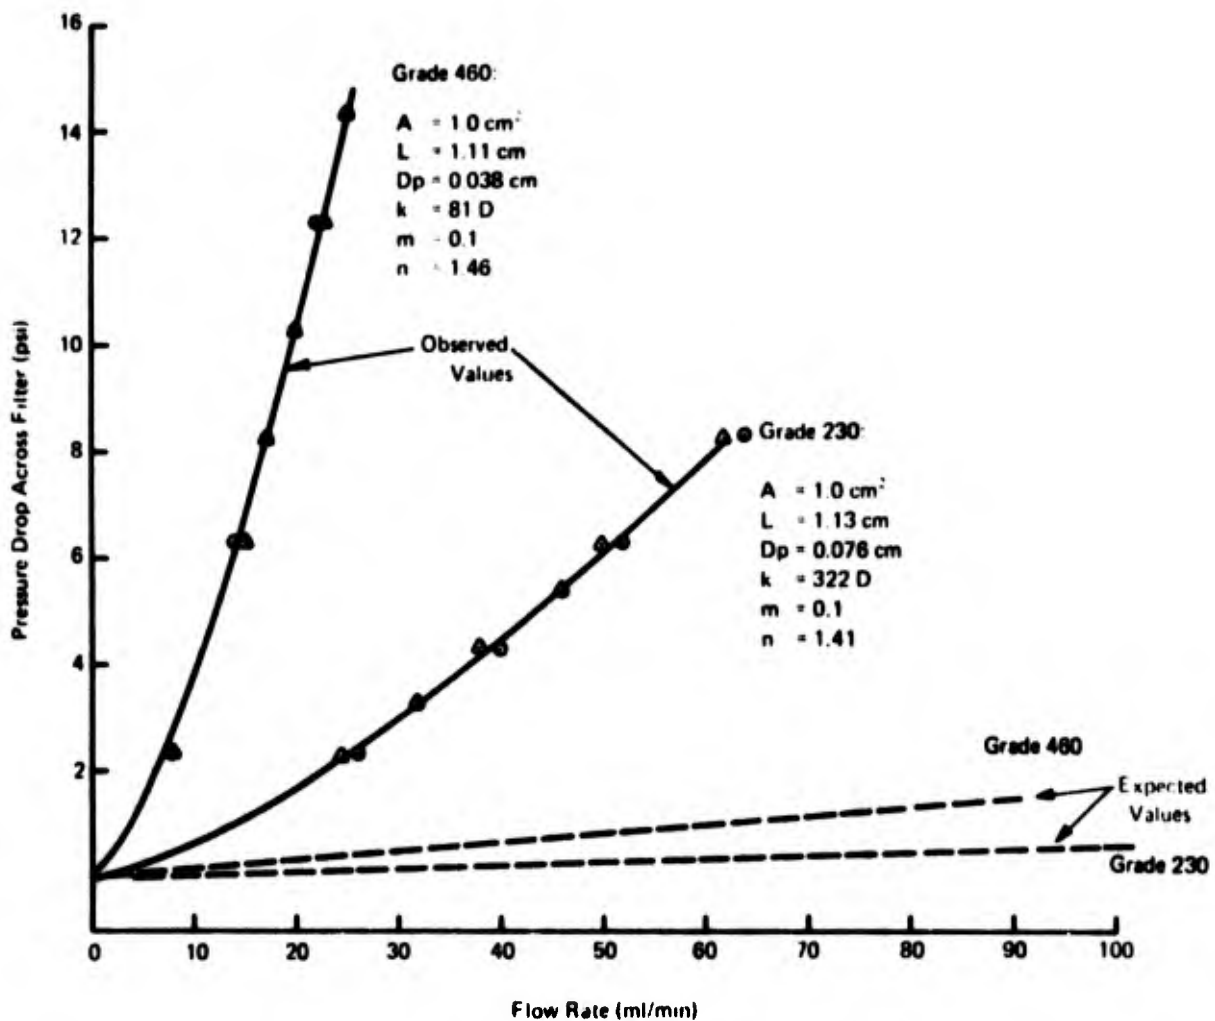


FIGURE 4. FLOW CHARACTERISTICS OF A 0.2-PERCENT AM-1 SOLUTION IN TWO DIFFERENT GRADE FILTERS

for a Newtonian liquid having the same shear viscosity as the polymer solution, the ratio of the observed to the expected pressure to produce a specified flow demonstrates the abnormally high resistance that these solutions exhibit in porous media. The curves drawn through these data were calculated by Equation 7 using the measured physical properties of the filters and assuming values for the Power Law Parameters. The best fit was obtained with $m = 0.15$ and $n = 1.46$ and 1.44 for the 460 and 230 grades, respectively. The higher n value indicates a slightly higher specific resistance in the smaller pores. Flow data were also obtained with filters having essentially the same permeabilities but different dimensions from those used in the first series of experiments. The results shown in Figure 4 yield very close to the same Power Law Parameters ($m = 0.15$ and $n = 1.46$ and $n = 1.41$). Thus, the anomalous resistance appears to be essentially independent of end effects.

In Figure 5 we have expressed the data in terms of the consistency variables defined by Equations 2 and 3. This approach shows that the Darcy Viscosity (Equation 4) or the resistance to flow is higher in the finer (460) grade filter but is essentially independent of the filter dimensions. While this is in agreement with our interpretation of the Power Law Model approach, we can make a quantitative comparison by choosing a particular shear stress or shear rate and calculating the Darcy Viscosity from Equations 4 and 8. Thus, from Figure 5 at a stress of 1000 dynes/cm^2 , the Darcy

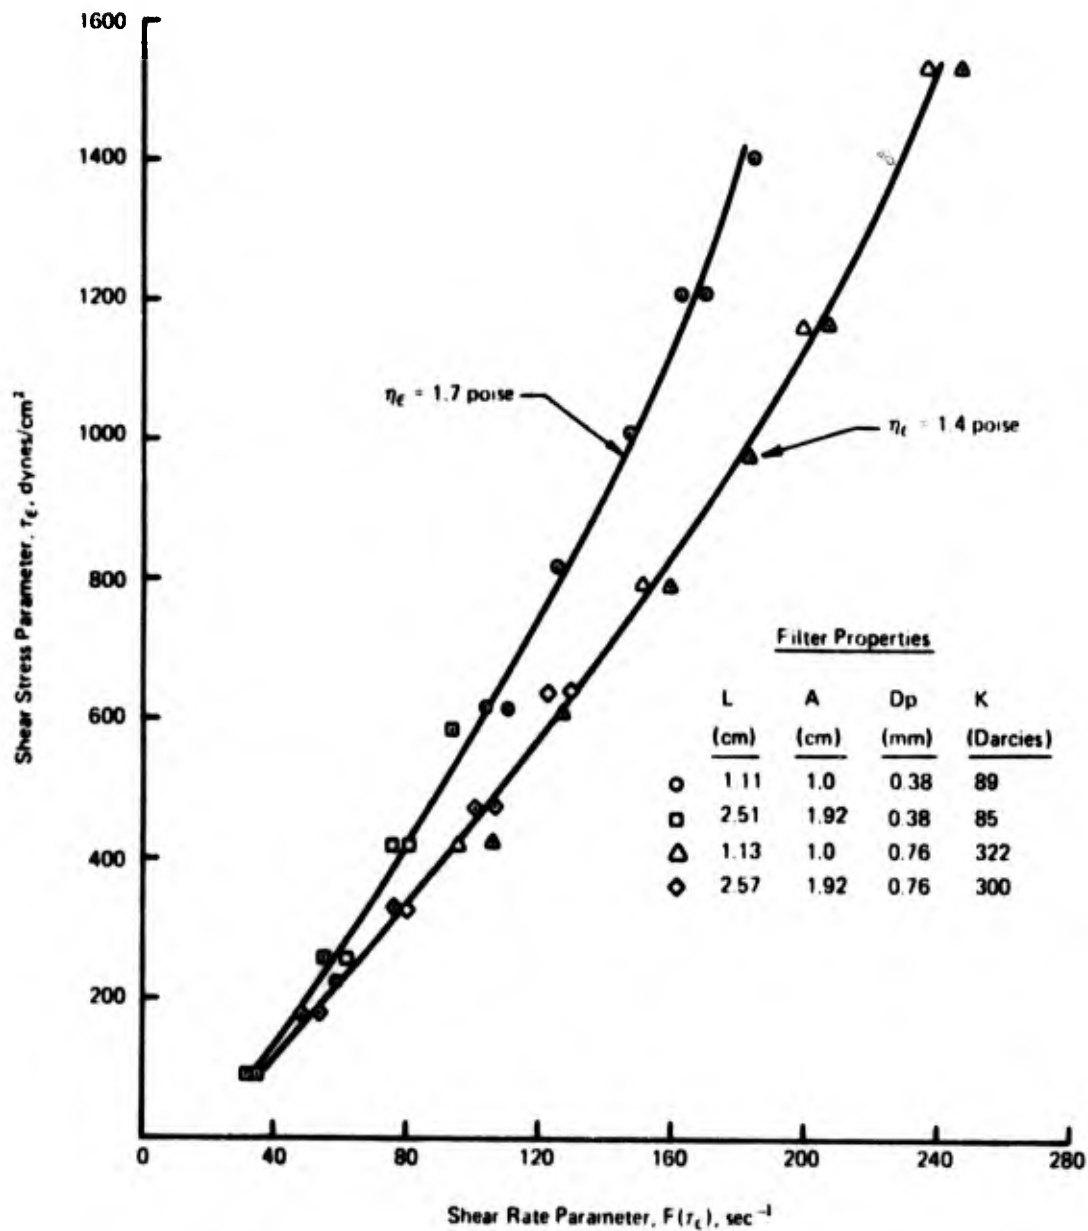


FIGURE 5. USE OF CONSISTENCY PARAMETERS FOR FLOW DATA IN DIFFERENT FILTERS

Viscosity is 1.7 and 1.4 poise for the 460- and 230-grade filters, respectively, whereas the Power Law Model calculates 1.8 and 1.5 poise. This small difference is very close to the experimental repeatability and can be attributed to the accuracy to which the Power Law Parameters were fit to the data.

In order to gain more confidence as to the repeatability of these results, additional data were obtained with several different filters. In the analysis of these results it has been assumed that filters within a given grade have the same average particle size. The results of these experiments, which are summarized in Table 3, confirm that the average Darcy Viscosity (at 1000 dynes/cm²) is 1.7 and 1.4 poise with a standard deviation of 0.05 and 0.07 poise for a 0.2-percent AM-1 solution in the 460- and 230-grade filters. When one considers that the shear viscosity of this solution is only 0.056 poise, it is evident that the elastic resistance of this solution in these porous media is from 25 to 30 times the viscous resistance.

TABLE 3. FLOW PROPERTIES OF A 0.2-PERCENT AM-1 SOLUTION IN DIFFERENT FILTERS

Filter Properties				Power Law Parameters		Darcy Viscosity
<i>L</i> (cm)	<i>A</i> (cm ²)	<i>D_p</i> (cm)	<i>K</i> (Darcies)	<i>m</i>	<i>n</i>	<i>N</i> (@ 1000 dynes/cm ²) (poise)
<i>Grade 460</i>						
2.51	1.92	0.038	85	0.10	1.46	1.69
1.11	1.0	0.038	70	0.10	1.45	1.70
1.11	1.0	0.038	72	0.10	1.48	1.74
1.11	1.0	0.038	82	0.10	1.46	1.66
1.11	1.0	0.038	88	0.09	1.46	1.58
1.11	1.0	0.038	89	0.10	1.46	1.69
				0.10	1.46	1.68 Std. Dev. = 0.05
<i>Grade 230</i>						
2.57	1.92	0.076	300	0.10	1.44	1.36
1.13	1.0	0.076	310	0.10	1.40	1.32
1.13	1.0	0.076	313	0.10	1.41	1.38
1.13	1.0	0.076	317	0.10	1.41	1.34
1.13	1.0	0.076	318	0.10	1.43	1.51
1.13	1.0	0.076	322	0.10	1.41	1.36
				0.10	1.42	1.38 Std. Dev. = 0.07

TABLE 4. POWER LAW PARAMETERS FOR TWO 0.2-PERCENT AM-1 SOLUTIONS HAVING THE SAME SHEAR VISCOSITY AND GUM CONTENT

Filter Properties				0.2% AM-1		Power Law Parameters	
<i>L</i> (cm)	<i>A</i> (cm ²)	<i>D_p</i> (cm)	<i>K</i> (Darcies)	viscosity (cp)	Gum (mg)	<i>m</i> 0.10	<i>n</i> 1.45
1.11	1.0	0.038	89	5.43	170.0	0.10	1.45
1.11	1.0	0.038	89	5.44	169.2	0.15	1.48
1.13	1.0	0.076	322	5.43	170.0	0.10	1.41
1.13	1.0	0.076	322	5.44	169.2	0.15	1.41

It is important to point out that while excellent repeatability (5 percent of the mean) was obtained when flow measurements were made in different filters with a given solution of AM-1, in some instances solutions made from different batches of AM-1 but having the same amount of AM-1 (as indicated by the gum content and shear viscosity) exhibited significantly different rheological behavior with the same filter (see Table 4). While the exact causes of these differences have not been established, it is known that this additive has a rather wide molecular weight distribution. Consequently, trace amounts of a very high molecular weight species could have little or no effect on gum content or shear viscosity and yet have a significant effect on elasticity. In any event, it is interesting to note that this simple experiment is able to detect differences in rheological behavior that would not have been expected from any other measurements. Whether or not these differences are important to fuel safety is not presently known.

The effect of additive content was studied by diluting a 0.2-percent AM-1 solution with JP-8 to make 0.1-percent, 0.05-percent and 0.025-percent solutions. As expected, the Darcy Viscosity

decreased with each dilution and in each instance the resistance was still slightly higher in the finer filter. By expressing these results in terms of a relative fluidity (i.e., the resistance of JP-8 relative to the resistance of the polymer solution), we can compare the effects of additive content on Darcy Viscosity and mist flammability by means of the Mist Flashback Test.⁽⁸⁾ In Figure 6 the relative Darcy

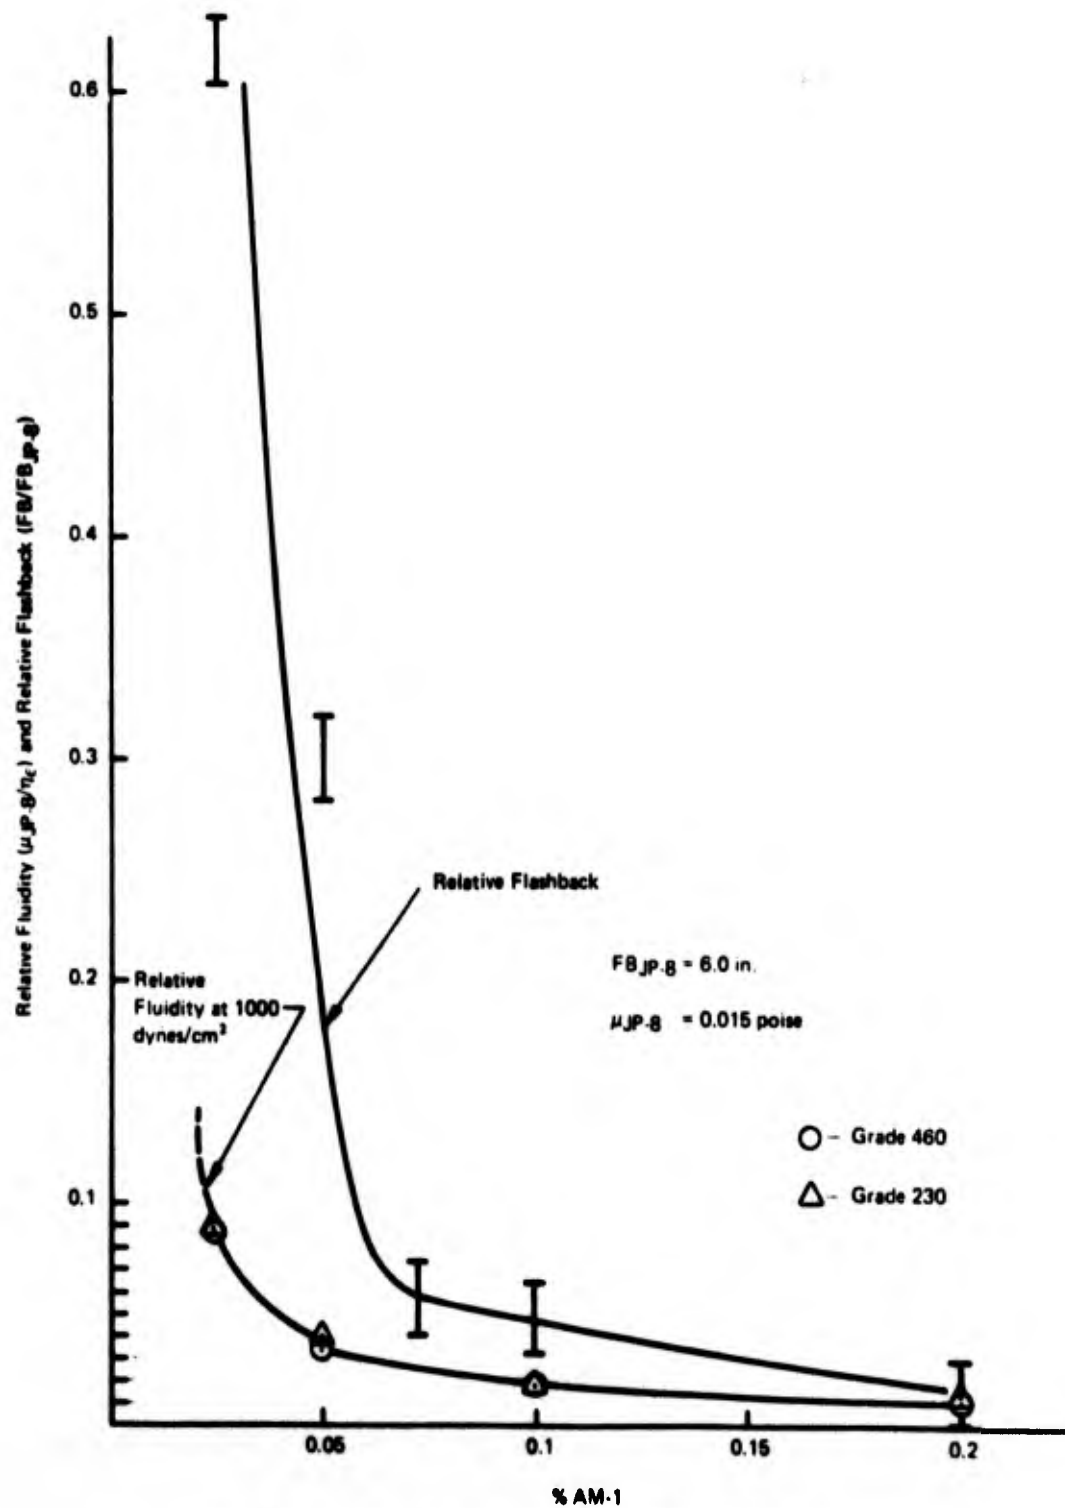


FIGURE 6. EFFECT OF AM-1 CONTENT ON RELATIVE FLUIDITY AND RELATIVE FLASHBACK

fluidity (at a shear stress of 1000 dynes/cm²) and the relative flashback (i.e., the flashback of the solution relative to JP-8) data are compared as a function of AM-1 content. These results show that there is a close correspondence between the relative flashback and relative fluidity particularly in the range of 0.07 to 0.2 percent. Below 0.07 percent the relative flashback increases rapidly, while this critical concentration appears to be slightly lower (0.05 percent) for the relative fluidity. This difference could possibly be explained by the fact that the mist flashback test has been optimized to produce maximum sensitivity. Since the relative resistance is a function of the shear stress, it is quite possible it would be more sensitive to this critical concentration if measurements were compared at different stress levels. Nevertheless, in the region of interest (0.07 to 0.2 percent AM-1), the two measurements appear to be related.

SUMMARY AND CONCLUSIONS

It has been found that the addition of 0.2-percent AM-1 to JP-8 produces a solution that exhibits a relatively low and essentially shear independent viscosity; however, this same solution offers an unusually high resistance (25 to 30 times higher than we would expect from the viscosity) to flow through metal filters consisting of nearly spherical particles. These results are in agreement with rheological theories that predict that a viscoelastic liquid may appear to have a low Newtonian viscosity in steady shear experiments and to have a high elongational viscosity that increases with the rate of elongation. With particle shape held approximately constant, the specific resistance (or Darcy Viscosity) appears to be slightly higher in the finer pores; however, the high degree of repeatability and the absence of hysteresis or time effects in the flow data essentially rule out filter plugging as the reason for the anomalous resistance. Furthermore, viscosity measurements in different capillary tubes, intermediate in size between the fine and coarse pore size filters used in these experiments, gave no indication that adsorption of the polymer could be a significant factor in changing the pore size. The use of either Power Law Parameters or consistency variables produces equivalent results, and while they are not capable of predicting the high resistance, a priori, they do serve as a means for comparing data from different filters.

The effect of additive content on the relative fluidity of AM-1 solutions is very similar to the effect on mist flammability. The primary difference appears to be in the exact location of the critical concentration, i.e., the concentration below which these measurements show a disproportionately large increase. For mist flammability, this occurs at 0.07-percent AM-1, while for relative fluidity, the critical concentration is about 0.05 percent. It is possible that closer agreement could be obtained if the relative fluidity were compared over a wide range of stresses rather than at the value of 1000 dynes/cm² that was used here.

The results of this study suggest that it may be feasible to develop a nondestructive (i.e., nonburning) fluid flammability evaluation technique. In other words, antimist effectiveness of dilute solutions of high molecular weight polymers may be evaluated by simple measurements of the solution's resistance to flow through a porous medium.

REFERENCES

1. Weatherford, W.D., Jr. and Wright, B.R., 45th Meeting of the AGARD/NATO Propulsion and Energetics Panel, Aircraft Fire Safety, Rome, Italy, 7-11 April, 1975.
2. Goldin, M., et al, *Chem. Engr. J.*, 4, 8 (1972).

3. Goldin, M., et al, *J. Fluid Mech.*, **38**, 689 (1969).
4. Lodge, "Elastic Liquids," **116**, Academic Press. London and New York (1964).
5. Bueche, F., "Physical Properties of Polymers," **71**, Interscience Publishers (1962).
6. Hassager, O., *J. Chem. Phys.*, **60**, 2111 (1974).
7. Marshall, R.J., and Metzner, A.B., *Ind. Engr. Chem. Fund.*, **5-6**, 393 (1967).
8. Christopher, R.J. and Middleman, S., *I&EC Fundamentals*, **4**, 422 (1965).
9. Wright, B.R., et al, Interim Report, AFLRL No. 25 (1973).
10. Mannheimer, R.J., Final Report AFLRL No. 18 (1973).

DISTRIBUTION LIST

	<u>No. of Copies</u>		<u>No. of Copies</u>
<i>Department of Defense</i>			
Defense Documentation Center Cameron Station Alexandria, Virginia 22314	12	Director of Defense Research & Engineering (OSD) ATTN: Dep Dir/Research & Technology Washington, D. C. 20301	1
Defense Fuel Supply Center Office of Technical Services ATTN: DFSC-TC Cameron Station Alexandria, Virginia 22314	3	Office of the Assistant Secretary of Defense ATTN: Technical Advisory Panel on Fuels & Lubricants Washington, D. C. 20301	1
<i>Department of the Army</i>			
Commander U. S. Army Materiel Command ATTN: AMCRD-TC AMCMA-V AMCSU-I 5001 Eisenhower Road Alexandria, Virginia 22333	1 1 1	Commander U. S. Army Munitions Command Picatinny Arsenal ATTN: SMUPA-D Dover, New Jersey 07801	1
Commander U. S. Army Armament Command ATTN: AMSAR-RE AMSAR-SM AMSAR-PP Rock Island, Illinois 61201	1 1 1	Commander Watervliet Arsenal ATTN: SMESV-RDR Watervliet, New York 12180	1
Commander U. S. Army Missile Command ATTN: AMSMI-RSM AMSMI-RRS Redstone Arsenal, Alabama 35809	1 1	Commander Frankford Arsenal ATTN: SMUFA-L6000 SMUFA-L1000 Library, C2500 Philadelphia, Pennsylvania 19317	1 1 1
Commander Anniston Army Depot ATTN: Chemical Laboratory Anniston, Alabama 36202	1	Commander U. S. Army Aviation Systems Command ATTN: AMSAV-R-R Old Mart Building 12th & Spruce Streets St. Louis, Missouri 63166	1
Commander USAGMPA Petroleum Field Office (East) ATTN: STSGP-PE, Bldg. 85-3 New Cumberland Army Depot New Cumberland, Pennsylvania 17070	1	Commander White Sands Missile Range ATTN: ORDBS-OM-Electro-Mechanical Labs ORDBS-OM-Systems Test Division ORDBS-OM White Sands, New Mexico 88002	1 1 1
Commander U. S. Army General Materials & Petroleum Agency ATTN: STSGP-SW Sharpe Army Depot Lathrop, California 95330	1	Commander U. S. Army Mobility Equipment Research & Development Center ATTN: AMXFB-GL AMXFB-GF Fort Belvoir, Virginia 22060	5 1
Commander U. S. Army Tank-Automotive Command ATTN: AMSTA-RKMT AMSTA-RHFL AMSTA-RGP AMSTA-QE Warren, Michigan 48090	1 1 1 1	Commander Corpus Christi Army Depot Naval Air Station ATTN: AMSAC-Q Corpus Christi, Texas 78419	1

	<u>No. of Copies</u>		<u>No. of Copies</u>
<i>Department of the Army (Cont'd)</i>			
Commander U. S. Army Foreign Science & Technology Center Federal Bldg. ATTN: AMXST-GE Charlottesville, Virginia 22901	1	Commander U. S. Army Aviation School ATTN: Office of the Librarian Fort Rucker, Alabama 36362	1
Commander U. S. Army Materials & Mechanics Research Center ATTN: AMXMR-TMS Watertown, Massachusetts 02172	1	Commander U. S. Army Chemical Research & Development Laboratories ATTN: Directorate of Weapons Systems (SMUCR-WS) Edgewood Arsenal, Aberdeen Proving Ground, Maryland 21010	1
Commander U. S. Army Troop Support Command ATTN: Technical Library 4300 Goodfellow Blvd. St. Louis, Missouri 63120	1	Commander U. S. Army Arctic Test Activity APO 731 Seattle, Washington 98731	1
Director Materiel Test Directorate Building 400 Aberdeen Proving Ground, Maryland 21005		Commander U. S. Army Alaska Support Command ATTN: ARCL-Q APO Seattle, Washington 98749	1
Commander U. S. Army Mobility R&D Laboratory Eustis Directorate ATTN: SAVDL-EU-SS Ft. Eustis, Virginia 23604	1	Commander U. S. Natick Development Center ATTN: AMXNM-YPB Natick, Massachusetts 01760	5
Technical Library Aberdeen Proving Ground, Maryland 21005	1	President U. S. Army Armor & Engineer Board ATTN: STEBB-EN Fort Knox, Kentucky 40121	1
Deputy Chief of Staff Research, Development & Acquisition Department of the Army ATTN: DAMA-CSS Washington, D. C. 20310	1	Commander Yuma Proving Ground ATTN: STEYT-MTS STEYT-MTM STEYP-MLS Yuma, Arizona 85369	1 1 1
Commander U. S. Army Ballistic Research Laboratory ATTN: AMX-RD-BTL, J. Dehn Aberdeen Proving Ground, Maryland 21005	1	Corp of Engineers Washington Aqueduct Division 5900 MacArthur Blvd. Washington, D. C. 20315	1
Commander U. S. Army Research Office (Durham) Box CM, Duke Station Durham, North Carolina 27706	1		

Department of the Navy

Commander U. S. Naval Air Systems Command ATTN: AIR 53451B AIR 5365 Washington, D. C. 20360	1	Commander Naval Ordnance Systems Command ATTN: Technical Library (ORD-9132) Washington, D. C. 20360	2
Commander Naval Air Development Center Code MACO Warminster, Pennsylvania 18974	1	Director U. S. Naval Research Laboratory ATTN: Code 6200 Code 6180 Washington, D. C. 20390	1 1

No. of
Copies

No. of
Copies

Department of the Navy (Cont'd)

Superintendent
U. S. Naval Post Graduate School
ATTN: Technical Reports Section
Monterey, California 93940

1

Naval Ship Engineering Center
Department of the Navy
ATTN: SEC 6101E
Washington, D. C. 20360

1

Commander
U. S. Naval Air Station
Overhaul & Repair Department
North Island
San Diego, California 92135

1

Commander
Naval Ship Engineering Center
Code 6101F
Center Bldg.
Prince George's Center
Hyattsville, Maryland 20782

1

Commander
U. S. Naval Civil Engineering Laboratory
Port Hueneme, California 93041

1

Commander
Naval Ship R & D Center
Annapolis Laboratory
ATTN: Code 2831

1

Commandant
U. S. Marine Corps
ATTN: Code AX
Code A04H
Washington, D. C. 20360

1

Technical Library
Annapolis, Maryland 21402

1

Commander
Naval Facilities Engineering Command
Transportation Maintenance
Management Branch
ATTN: Code 10332
Washington, D. C. 20390

1

Department of the Air Force

Commander
Air Force Materials Laboratory (AFSC)
ATTN: AFML/SFF
Wright-Patterson Air Force Base, Ohio 45433

2

Headquarters
U. S. Air Force RDPS
Washington, D. C. 20310

1

Commander
Headquarters
San Antonio Air Material Area
ATTN: SAAMA (SAOQ)
Kelly Air Force Base, Texas 78241

1

Other Government Agencies

Scientific & Technical Information Facility
P. O. Box 33
ATTN: NASA Representative (SAK/DL)
College Park, Maryland 20740

1

Federal Aviation Administration
2100 Second Street, S. W.
ATTN: Aircraft Design Criteria Branch,
Code ARD-520
Washington, D. C. 20591

2

Federal Aviation Administration
800 Independence Avenue, S. W.
ATTN: Administrative Standards
Division (MS-110)
Washington, D. C. 20590

2