


AD-A037 701

ARMY ELECTRONICS TECHNOLOGY AND DEVICES LAB FORT MON--ETC F/G 10/3
LITHIUM BATTERY SESSION. SECONDARY BATTERIES. SECONDARY LITHIUM--ETC(U)
1974 M SALOMON

UNCLASSIFIED


NL

| OF |
AD
A037 701

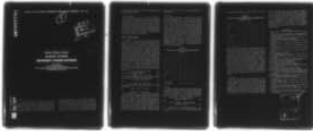

END

DATE
FILMED
4-77

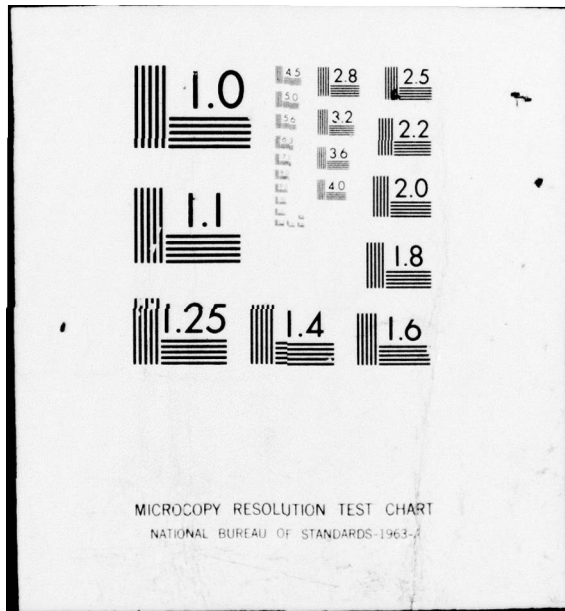

1.0 4.5 2.8 2.5
5.0 3.2 2.2
3.6 2.0
4.0 1.8
1.1
1.25 1.4 1.6

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

ADA03701

Reprinted from 26th ANNUAL PROCEEDINGS POWER SOURCES CONFERENCE - May, 1974

5

DDC
APR 5 1977
C

11 1971
12 3p.

Lithium Battery Session
SECONDARY BATTERIES
SECONDARY LITHIUM BATTERIES

10 Mark Salomon
Power Sources Technical Area
U.S. Army Electronics Technology and Devices Laboratory (ECOM)
Fort Monmouth, New Jersey

DDC FILE COPY

Introduction

In 1803, Johann Ritter discovered the concept of the storage battery; by the year 1900, all our presently used secondary battery systems had been developed and a good deal of technology had evolved. It was not until the early 1960's that new concepts for secondary systems emerged. The secondary lithium battery is one such concept that appears very

attractive both for military and non-military use. Although an operational room temperature secondary battery has not been demonstrated to date, it must be recalled that it took almost 30 years to commercially develop the lead-acid battery from the time of its discovery in 1859 by Gaston Planté. The problems encountered in developing a room temperature secondary lithium battery are now quite well known; some of these

390007

int


problems are discussed below and some investigations carried out at ECCM are reviewed.

Technical Discussion


General: In previous works, it was found that lithium is not generally stable in aprotic solvents but does react with such solvents as PC^{*2-4} and DMF^{**5,6}. It has also been found that the trace water present in these organic solvents can lead to both film formation and decreasing limiting currents.⁷⁻¹¹ Thus, the stability of the lithium in aprotic organic solvents has turned out to be a complex problem and a considerable amount of basic work remains to be done before practicality is achieved. It does appear, however, that the presence of SO₂ stabilizes the Li-anode in most aprotic solvents.¹²

*PC = propylene carbonate
**DMF = dimethyl formamide


In addition to these and other problems associated with lithium anodes, a secondary cathode has proved to be a major problem. A number of metal halides,¹²⁻¹⁴ sulfides,^{15,16} and quinones¹⁷ are some of the cathodes that have been proposed. Secondary lithium batteries utilizing metal halide cathodes are very attractive; the energy densities are high, the materials are readily available, and they appear to be highly reversible. The major problem associated with metal halides is their high solubility. The present work was initiated in the hope that the solubility problem could be understood and, eventually, prevented. Although the present work deals with silver halides which are, energetically, borderline as cathode materials, they are representative of the class of metal halides known as soft acids; i.e., Ag⁺ is a "soft-acid" in the Pearson sense¹⁸ and is representative of the typical soft-acids such as Cu⁺, Hg⁺, Tl⁺, Cd²⁺, Tl³⁺, etc. The divalent cations of Fe, Co, Ni, and Cu are, behaviorally, borderline between hard and soft.¹⁸ Consider the cell




for which the overall cell reaction is




Self discharge of the anode can occur if the cathode is soluble, the two major mechanisms of self discharge being




and



The major equilibria involving solubilization of the cathode are, therefore,



and



The inability to develop a well behaved secondary lithium/metal halide battery is attributable to the large values of K₈₂. Attempts have been made to suppress reaction (5) by the addition of a "hard-acid", such as AlCl₃, which very effectively removes free halide in solution by forming AlCl₄⁻. This approach can lead to serious limitations such as deposition of Al at the anode, and inability to recharge the cathode. In the present approach, this problem is studied in terms of ion solvent interactions. By using mixed aprotic solvents, it is hoped that the Cl⁻ ion may be weakly stabilized in solution (rather

than forming AlCl₄⁻) and at the same time, the AgCl₂⁻ ion is destabilized.

Experimental

The complex solubilities of AgCl, AgBr, and AgI were determined potentiometrically by titrating a halide solution with standard AgClO₄. A silver wire was used as the indicator electrode and the reference electrode was Ag/Ag⁺ separated by a salt bridge. Tetrapropyl ammonium salts were used to maintain a constant ionic strength, usually 0.1000 M, throughout the titration. All salts were purified by the methods described by Mann¹⁹ and the solvents were purified by fractional distillation. The titration vessels were fitted with ground glass joints and were assembled and sealed in a dry box. The emf measurements were recorded at 25 ± 0.1°C. The stability constants and solubility constants were calculated by an iterative method.^{20,21} The solvent systems studied were mixtures of propionitrile with SO₂ (PN/SO₂), propylene carbonate with tetrahydrothiophene, (PC/THT), and acetone with water, (AC/H₂O). The results are given in Table I along with some data from other investigations.

TABLE I
VALUES OF K₈₀ AND K₈₂ IN SEVERAL SOLVENTS
AT 25°C

SOLVENT	- LOG K ₈₀			LOG K ₈₂		
	Cl	Br	I	Cl	Br	I
PC ^a	20.2	20.6	20.8	1.0	0.3	1.3
PC-THT (0.09 M)	12.1	12.5	13.7	1.0	0.7	0.8
PC-THT (0.56 M)	9.4	10.0	10.9	1.1	1.0	1.4
PN	15.3	16.0	17.1	1.7	1.3	1.2
PN-SO ₂ (0.95 M)	11.5	12.6	14.6	-1.6	-1.5	-0.8
PN-SO ₂ (3.30 M)	10.4	11.5	13.7	-2.5	-2.4	-2.3
AC	21.2	21.6	23.0	1.6	1.7	1.4
AC-H ₂ O (0.55 M)	19.9	20.6	22.0	1.2	1.2	1.1
AC-H ₂ O (3.95)	15.2	16.6	19.0	-0.6	-0.2	0.3
AC-H ₂ O (9.36 M)	13.4	15.0	17.8	-1.6	-1.8	-0.6
DMSO ^b	10.6	10.6	11.6	1.6	1.1	1.2
H ₂ O ^c	9.8	12.3	16.0	-4.4	-4.7	-4.8

^a. FROM REFERENCE 22.

^b. FROM REFERENCE 23.

^c. FROM REFERENCE 24.

ALL OTHER DATA ARE THE PRESENT RESULTS.

Discussion

The effect of solvent composition on the various equilibria is quite large. To determine the specific effect on each ion, one can examine the individual ionic free energies of transfer, ΔG_t^o(ion), from water to the specific solvent s. The extra-thermodynamic assumption²⁵ used to evaluate ΔG_t^o(Ag⁺) is

$$\Delta G_t^o(\text{Ag}^+) = (\Delta G_t^o(\text{Ag}^+, \text{AgCl}_2^-) + \Delta G_t^o(\text{Ag}^+, \text{AgBr}_2^-))/2 \quad (6)$$

where

$$\Delta G_t^o(\text{Ag}^+, \text{AgX}_2^-) = 2.3RT (\log (K_{82,w} K_{80,w}/K_{82,s} \cdot K_{80,s})) \quad (7)$$

and

$$\Delta G_t^o(\text{Ag}^+, \text{X}^-) = 2.3RT \log (K_{80,w}/K_{80,s}) \quad (8)$$

In Equations (7) and (8), X = Cl or Br. The results for the

individual $\Delta G_i^\circ(\text{ion})$ values are given in Table II. It is noted

TABLE II
SINGLE ION FREE ENERGIES OF TRANSFER FROM
WATER AT 25°C

SOLVENT	$\Delta G_i^\circ(\text{ION})$				
	Ag^+	Cl^-	Br^-	AgCl_2^-	AgBr^-
METH	2.2	2.7	2.2	3.0	1.8
DMF	-3.1	10.0	7.2	2.1	-1.4
DMSO	-7.6	8.7	5.6	0.6	-2.6
PN	-2.0	9.5	7.0	1.2	-1.2
PN-SO ₂ (0.95 M)	-2.8	5.1	3.2	1.2	-1.2
PN-SO ₂ (3.30 M)	-3.0	3.8	1.9	1.2	-1.2
PC	5.3	8.6	6.0	1.5	-0.8
PC-THT (0.09 M)	-5.7	8.8	0.9	1.4	-1.4
PC-THT (0.56 M)	-9.5	9.0	1.4	1.4	-1.4

NOTE: $\Delta G_i^\circ(\text{ION})$ VALUES ARE IN K CAL MOL⁻¹.

that the Ag^+ ion is generally more stable in the aprotic solvent than in water while the reverse is true for the Cl^- ion. It is also seen that the anion stability increases in the aprotic solvent as the ionic radius increases. This effect is attributed to mutual polarization as discussed elsewhere.²³ The effects on Cl^- solvation appears, however, to be quite different. Addition of THT to the aprotic solvent has negligible effect on $\Delta G_i^\circ(\text{Cl}^-)$, whereas SO_2 additions significantly stabilize the Cl^- ion. This latter effect indicates the existence of an $\text{SO}_2\text{-Cl}^-$ complex which means that SO_2 can behave, simultaneously, as a strong Lewis base and a weak Lewis acid. Bonding of the $\text{SO}_2\text{-Cl}^-$ complex presumably occurs through the empty 3-p orbitals on the sulfur. The solvation of Cl^- with THT on the other hand occurs via interaction with the ring structure of THT and not with the S-atom. Additional work on these effects is in progress.

Conclusions

The addition of sulfides to the aprotic solvents is seen to display varying behavior. Both SO_2 and THT increase K_{s0} extremely rapidly even when present in small amounts. This is attributable²³ to π -bond formation between Ag^+ and the S-atom (this is in addition to the σ -bond). The interesting difference between the two systems lies in the fact that SO_2 additions to PN greatly reduce K_{s2} whereas THT additions to PC virtually has no effect on K_{s2} . It would appear, therefore, that in the presence of SO_2 , the Cl^- ion is stabilized by dipolar

coordination to SO_2 or by π -bonding. The dipolar coordination of Cl^- to PC and THT appears to be similar, resulting in little change in K_{s2} . This phenomenon is being investigated further to establish the site of Cl^- coordination and its nature (i.e., ionic, dipolar, covalent). The effect of H_2O additions to AC, PC,²⁰ and DMSO^{26,27} is much less than that of the corresponding sulfides. Thus, trace amounts of water in organic solvents should have a minimal effect on a metal-halide cathode but, as discussed above, its effects on the anode are quite important.

REFERENCES

- (a) F. Cajori, "A History of Physics," Macmillan, New York, 1899.
(b) M. Salomon, "Proc. Symp. Batteries for Transportation and Propulsion," The Electrochemical Society, Columbus Section, Columbus, Ohio, 1972.
- J. C. Synnott and J. N. Butler, Anal. Chem. **41**, 1890 (1969).
- M. Salomon, J. Phys. Chem., **74**, 2519 (1970).
- A. N. Dey and B. P. Sullivan, J. Electrochem. Soc., **117**, 222 (1970).
- J. N. Butler and J. C. Synnott, J. Am. Chem. Soc., **92**, 2602 (1970).
- K. B. Khyilstova and V. N. Korshunov, Elektrokimiya, **7**, 1022 (1971).
- D. R. Cogley and J. N. Butler, J. Phys. Chem., **72**, 4568 (1968); **73**, 4026 (1969).
- B. Burrows and S. Kirkland, J. Electrochem. Soc., **116**, 442 (1969).
- R. F. Scarr, *ibid.*, **117**, 295 (1970).
- B. K. Makarenko, Yu. M. Povarov, P. A. Sereda, and N. Yu. Bobrova, Elektrokimiya, **9**, 705 (1972).
- L. Heerman and J. Van Baelen, Bull. Soc. Chem. Belges, **81**, 379 (1972).
- D. L. Maricle and J. P. Mohns, Fr. Demande, 2014, 160 (1970).
- D. Herbert and J. Ulam, U.S. Patent 3,043,896 (1962).
- E. Buzzelli, U.S. Patent 3,489,296 (1969).
- M. L. B. Rao, U.S. Patent 3,413,154 (1968).
- D. A. Nole and V. Moss, U.S. Patent 3,532,543 (1970).
- H. Alt, H. Binder, A. Kohling and G. Sandstede, J. Electrochem. Soc., **118**, 1950 (1971).
- R. G. Pearson, J. Am. Chem. Soc., **85**, 3533 (1963).
- C. K. Mann, Adv. Electroanal. Chem., **3**, 57 (1969).
- J. N. Butler, D. R. Cogley, J. C. Synnott and G. Holleck, "Study of the Composition of Nonaqueous Solutions" Final Report, Air Force Contract No. AF 19(628)6131, Tyco Labs, Sept. 1969: AD No. 699-589.
- M. Salomon, ECOM Technical Report No. 4204, March, 1974.
- (a) J. N. Butler, Anal. Chem., **39**, 1799 (1967);
(b) J. Courtot-Corpez and M. L'Her, Bull. Soc. Chem., France, 675 (1969).
- (a) R. Alexander, E. C. Ko, Y. C. Mac and A. J. Parker, J. Am. Chem. Soc., **89**, 3703 (1967).
(b) M. K. Chantooni and I. M. Kolthoff, J. Phys. Chem., **77**, 1 (1973).
- L. G. Sillén and A. E. Martell, Stability Constants of Metal-Ion Complexes, The Chemical Society, London, 1964.
- M. Salomon and B. K. Stevenson, J. Phys. Chem., **77**, 3002 (1973).
- J. C. Synnott and J. N. Butler, *ibid.*, **73**, 1470 (1969).
- J. N. Butler, D. R. Cogley, and W. Zurosky, J. Electrochem. Soc., **115**, 445 (1968).

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DIC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	AVAIL. and/or SPECIAL
A	

