

AD-A039 367

MONSANTO RESEARCH CORP DAYTON OHIO DAYTON LAB
FLAME- AND SMOKE-RETARDANT POLYMER SYSTEMS.(U)
APR 77 L PARTS, C A THOMPSON


F/G 11/3

UNCLASSIFIED

N00024-76-C-5336

NL

| OF |
AD
A039 367

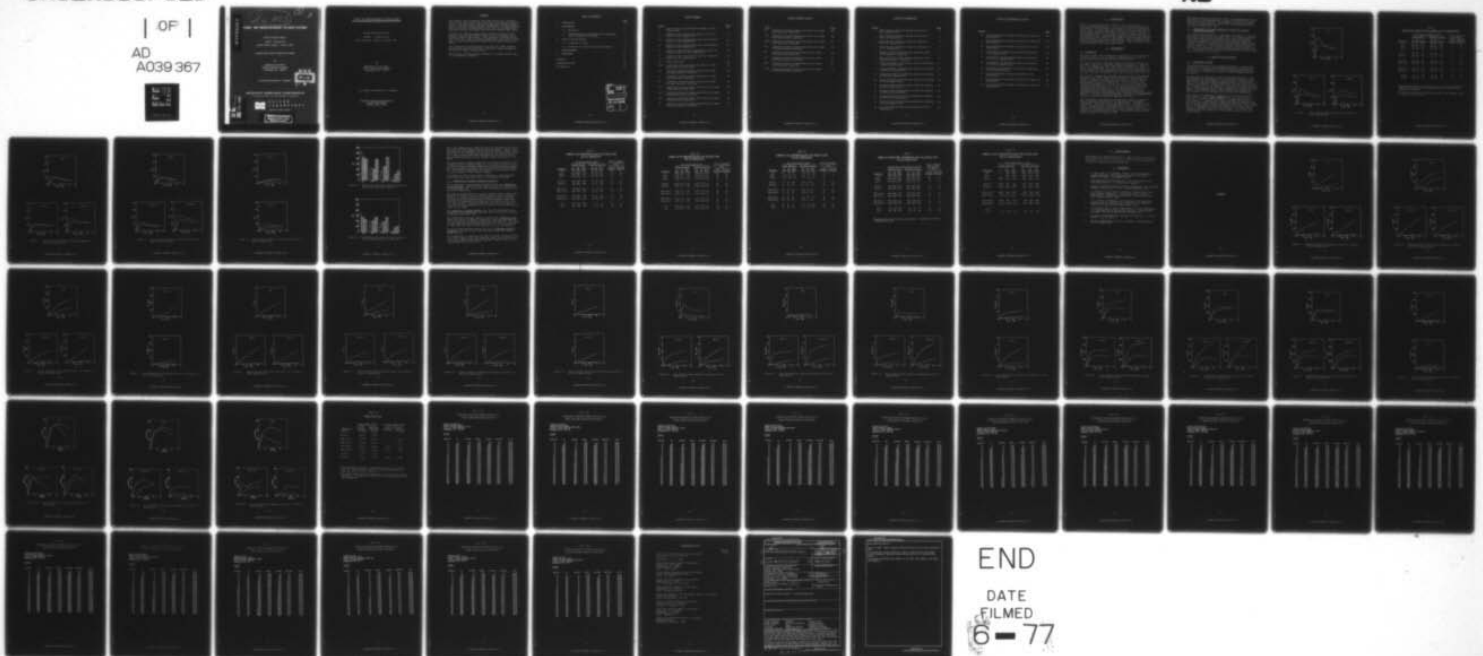

END
DATE
FILMED
6-77

AD A 039367

Lee 1473

11

2

FLAME- AND SMOKE-RETARDANT POLYMER SYSTEMS

Second Quarterly Report

Issued: 26 April 1977

Period Covered: August - October 1976

Prepared Under Contract: N00024-76-C-5336

For

Department of the Navy
Naval Sea Systems Command
Washington, DC 20362

Leo Parts and Catherine A. Thompson



MONSANTO RESEARCH CORPORATION


A SUBSIDIARY OF MONSANTO COMPANY



DAYTON
LABORATORY

DAYTON, OHIO 45407

AD No. _____
DDC FILE COPY

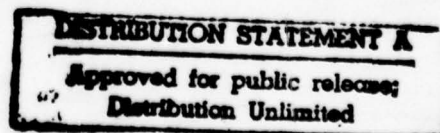

FLAME- AND SMOKE-RETARDANT POLYMER SYSTEMS

Second Quarterly Report

Issued: 26 April 1977

Period Covered: August - October 1976

For

Department of the Navy
Naval Sea Systems Command
Washington, DC 20362

Leo Parts and Catherine A. Thompson

MONSANTO RESEARCH CORPORATION
DAYTON LABORATORY
DAYTON, OHIO 45407

ABSTRACT

Experimental smoke-retardant PVC compositions and a reference base polymer were coated with alkyd- and epoxy-based intumescent paints. Specimens were tested in an NBS smoke density chamber under flame and nonflame exposure conditions. The smoke optical density, and the concentrations of CO, CO₂, NO_x, hydrocarbons, hydrogen chloride and oxygen were monitored during these tests.

Although the coatings reduced smoke formation from the base polymer, they had an adverse effect on the performance of the smoke-retardant compositions. The commercial coatings used in this work were found to generate significant quantities of smoke. Other, recently developed coatings will be used in projected work.

The intumescent coatings reduced the rates of carbon monoxide and hydrogen chloride formation, especially under nonflame exposure to a radiant energy source.

The coatings contributed small amounts of nitrogen oxides (NO_x) to the combustion products.

TABLE OF CONTENTS

	<u>Page</u>
1. INTRODUCTION	1
2. EXPERIMENTAL	1
2.1 Materials	1
2.2 Test Methods for the Formation of Smoke and Gaseous Combustion Products	2
3. RESULTS AND DISCUSSION	2
3.1 Formation of Smoke	2
3.2 Formation of Gaseous Combustion Products	9
4. ACKNOWLEDGMENT	15
5. REFERENCES	15
APPENDIX	16
DISTRIBUTION LIST	53
DD FORM 1473	54

ACCESSION for		
DTIC	White Section	☒
DOC	Buff Section	☐
UNANNOUNCED		☐
JUSTIFICATION		
BY		
DISTRIBUTION/AVAILABILITY CODES		
Dist.	AVAIL and/or SPECIAL	
A		

LIST OF TABLES

<u>Table</u>		<u>Page</u>
I	Smoke Optical Density Results Summary for PVC Compositions	4
II	Summary of CO Concentration Data for Selected Times for PVC Compositions	10
III	Summary of CO ₂ Concentration Data for Selected Times for PVC Compositions	11
IV	Summary of NO _x Concentration Data for Selected Times for PVC Compositions	12
V	Summary of Hydrocarbons Concentration Data for Selected Times for PVC Compositions	13
VI	Summary of HCl Concentration Data for Selected Times for PVC Compositions	14
VII	Sample Mass Data	36
VIII	Combustion Products Formed from BP-IC-1 Under Flame Exposure Conditions	37
IX	Combustion Products Formed from BP-IC-1 Under Nonflame Exposure Conditions	38
X	Combustion Products Formed from BP-IC-2 Under Flame Exposure Conditions	39
XI	Combustion Products Formed from BP-IC-2 Under Nonflame Exposure Conditions	40
XII	Combustion Products Formed from FSP-1-IC-1 Under Flame Exposure Conditions	41
XIII	Combustion Products Formed from FSP-1-IC-1 Under Nonflame Exposure Conditions	42
XIV	Combustion Products Formed from FSP-1-IC-2 Under Flame Exposure Conditions	43
XV	Combustion Products Formed from FSP-1-IC-2 Under Nonflame Exposure Conditions	44

LIST OF TABLES (cont'd)

<u>Table</u>		<u>Page</u>
XVI	Combustion Products Formed from FSP-2-IC-1 Under Flame Exposure Conditions	45
XVII	Combustion Products Formed from FSP-2-IC-1 Under Nonflame Exposure Conditions	46
XVIII	Combustion Products Formed from FSP-2-IC-2 Under Flame Exposure Conditions	47
XIX	Combustion Products Formed from FSP-2-IC-2 Under Nonflame Exposure Conditions	48
XX	Combustion Products Formed from Al-IC-1 Under Flame Exposure Conditions	49
XXI	Combustion Products Formed from Al-IC-1 Under Nonflame Exposure Conditions	50
XXII	Combustion Products Formed from Al-IC-2 Under Flame Exposure Conditions	51
XXIII	Combustion Products Formed from Al-IC-2 Under Nonflame Exposure Conditions	52

LIST OF ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	Smoke Optical Densities During the Burning of BP-IC Compositions	3
2	Smoke Optical Densities During the Burning of FSP-1-IC Composition	5
3	Smoke Optical Densities During the Burning of FSP-2-IC Compositions	6
4	Smoke Optical Densities During the Exposure of Al-IC Compositions	7
5	Maximum Specific Smoke Optical Densities Under Flame Exposure Conditions	8
6	Maximum Specific Smoke Optical Densities Under Nonflame Exposure Conditions	8
7	Carbon Monoxide Concentrations During the Burning of BP-IC Compositions	17
8	Carbon Monoxide Concentrations During the Burning of FSP-1-IC Compositions	18
9	Carbon Monoxide Concentrations During the Burning of FSP-2-IC Compositions	19
10	Carbon Monoxide Concentrations During the Exposure of Al-IC Compositions	20
11	Carbon Dioxide Concentrations During the Burning of BP-IC Compositions	21
12	Carbon Dioxide Concentrations During the Burning of FSP-1-IC Compositions	22
13	Carbon Dioxide Concentrations During the Burning of FSP-2-IC Compositions	23
14	Carbon Dioxide Concentrations During the Exposure of Al-IC Compositions	24
15	NO _x Concentrations During the Burning of BP-IC Compositions	25

LIST OF ILLUSTRATIONS (cont'd)

<u>Figure</u>		<u>Page</u>
16	NO _x Concentrations During the Burning of FSP-1-IC Compositions	26
17	NO _x Concentrations During the Burning of FSP-2-IC Compositions	27
18	NO _x Concentrations during the Exposure of Al-IC Compositions	28
19	Hydrocarbons Concentrations During the Burning of BP Compositions	29
20	Hydrocarbons Concentrations During the Burning of FSP-1-IC Compositions	30
21	Hydrocarbons Concentrations During the Burning of FSP-2-IC Compositions	31
22	Hydrocarbons Concentrations During the Exposure of Al-IC Compositions	32
23	HCl Concentrations During the Burning of BP Compositions	33
24	HCl Concentrations During the Burning of FSP-1-IC Compositions	34
25	HCl Concentrations During the Burning of FSP-2-IC Compositions	35

1. INTRODUCTION

Means for enhancing the fire safety of two polymeric materials, plasticized polyvinyl chloride (PVC) and Neoprene, are investigated in this program. As reported in our first quarterly report (Ref. 1) ferric and cupric acetylacetonates were found to reduce smoke formation from PVC, in terms of optical density, by approximately 55%. In an attempt to further enhance the fire performance of these compositions, they were coated with intumescent compositions. Data for the formation smoke and gaseous combustion products from these compositions, under controlled test conditions, are presented in this report. Flame propagation data will be presented in a subsequent report.

2. EXPERIMENTAL

2.1 MATERIALS

The base polymer (BP) formulation contained 30 phr of Santicizer 148 plasticizer, 7 phr of dibasic lead phthalate, 0.4 phr of dibasic lead stearate and 0.4 phr of stearic acid.

The flame- and smoke-retardant (FSR) formulations contained 30 phr $MgCO_3$ (Magcarb L, from Merck Chemical Division). Additionally, the formulations FSP-1 and FSP-2 contained also 5 phr ferric acetylacetonate and cupric acetylacetonate, respectively. The procedure for the preparation of the 0.16 cm thick sheets of the three polymer compositions was reported previously (Ref. 1).

Two types of intumescent coatings, an alkyd- and an epoxy-based material, were used. These were applied onto one side of the molded PVC sheet specimens and of a 0.019 in. thick aluminum sheet according to the manufacturers' specifications. The alkyd-based intumescent coating (No. 110 by C. M. Athey Paint Company) is designated as IC-1 in the present data tabulations. The epoxy-based coating (No. 477 by Ocean Chemicals, Inc.) is identified by the suffix IC-2. The alkyd-based coating is recommended by its manufacturer for interior surfaces (e.g., galleys, and engine room bulkheads and overheads) of marine vessels (Ref. 2). The epoxy-based intumescent coating is recommended for interior, exterior, and marine applications (Ref. 3).

The intumescent coatings were applied with a brush in approximate thicknesses specified in the manufacturers' technical literature. The alkyd coating is applied at a coverage of 200 square feet per gallon in a single application. The epoxy coating is recommended at a thickness of 9 to 10 mils, which is attained in two applications, at a total coverage rate of approximately 130 square feet per gallon. The solids content of the epoxy coating is in excess of 80%.

The alkyd coating was allowed to dry at room temperature for one week and the epoxy coating for at least two weeks before specimens were cut for testing. The thickness of the dried alkyd coating was approximately 15 mils; the corresponding value for the epoxy coating was 9 mils.

2.2 TEST METHODS FOR THE FORMATION OF SMOKE AND GASEOUS COMBUSTION PRODUCTS

An analysis system capable of continuous measurement of CO, CO₂, NO_x, total hydrocarbons and oxygen (Ref. 4) during the burning of polymers was used in conjunction with smoke measurements. This system, designed and constructed at Monsanto Research Corporation (MRC), is connected to the NBS-Aminco smoke density chamber, that is utilized for the burning of samples under controlled conditions. The apparatus and the test methods were described in some detail in the preceding quarterly report (Ref. 1). The sample sizes and the test conditions were identical with those specified in that report.

3. RESULTS AND DISCUSSION

3.1 FORMATION OF SMOKE

The primary objective of the present program is to lower smoke formation from burning PVC and Neoprene polymer compositions. Concomitantly, enhancement of other fire performance characteristics (e.g., reduction of the rate of flame propagation) will be sought.

Previous work at MRC (Ref. 5 and 6) and elsewhere (Ref. 7) has demonstrated the effectiveness of intumescent coatings for enhancing the fire performance of some polymers. Upon exposure to heat, the intumescent coatings expand to 100-300 fold of their original thicknesses, forming insulating cellular structures that afford protection to the substrate. Reduction of smoke formation and of flame propagation has been attained with intumescent coatings. In the present work, it was sought to investigate the effectiveness of that approach with the FSR PVC compositions.

Both types of intumescent coatings used in the present work, were found to reduce smoke formation from the base polymer, in terms of its maximum optical density, by approximately 20% (see Figure 1). However, when these coatings were applied onto the fire- and smoke-retardant compositions FSP-1 and FSP-2, they had an adverse effect on smoke formation (see Table I and Figures 2-6). It appeared that with these materials, of lower smoke formation propensity than the base polymer, the coatings contributed smoke upon exposure to the radiant energy source and to the flame.

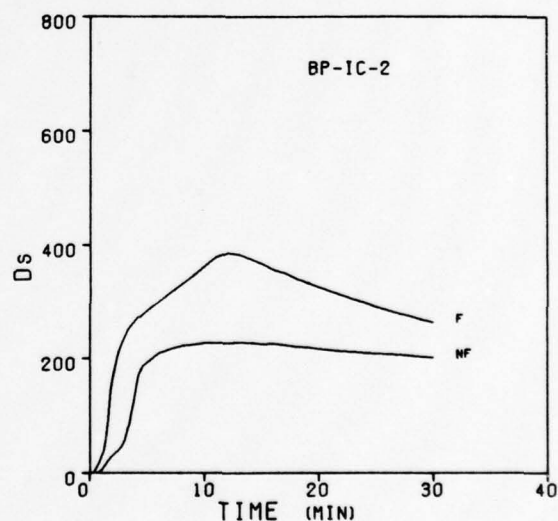
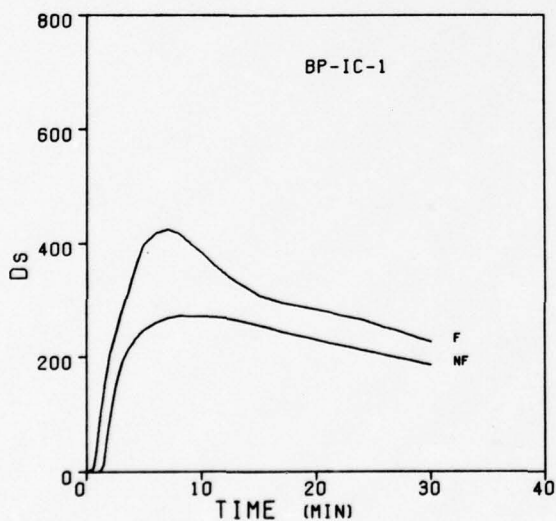
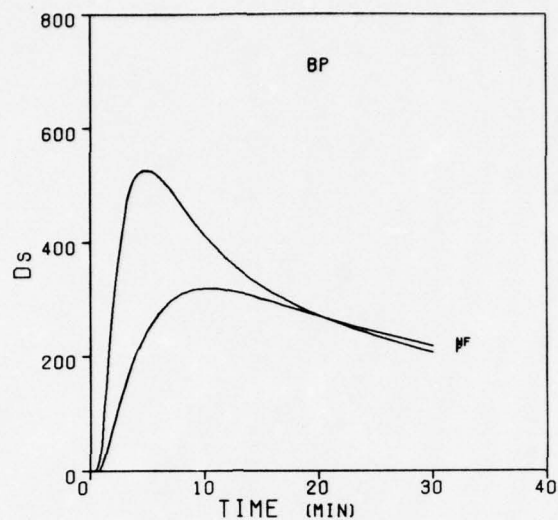


Figure 1. Smoke Optical Densities During the Burning of BP-IC Compositions

Table I

SMOKE OPTICAL DENSITY RESULTS SUMMARY FOR PVC COMPOSITIONS^a

<u>Material</u>	<u>Smoke Optical Density (SOD)</u>						<u>Time to Maximum SOD (min)</u>	
	<u>Flame Exposure</u>			<u>Nonflame Exposure</u>			<u>Flame Exposure</u>	<u>Nonflame Exposure</u>
	<u>10 min</u>	<u>20 min</u>	<u>Maximum</u>	<u>10 min</u>	<u>20 min</u>	<u>Maximum</u>		
BP	410	270	510	320	270	320	4	10
FSP-1	185	135	200	180	155	185	6	12
FSP-2	140	105	165	150	115	155	5	8
BP-IC-1	380	280	420	270	230	270	7	8
BP-IC-2	360	320	390	230	220	230	12	13
FSP-1-IC-1	200	180	200	195	190	200	11	15
FSP-1-IC-2	340	260	380	270	270	270	7	16
FSP-2-IC-1	200	135	250	180	150	180	6	12
FSP-2-IC-2	410	320	420	270	240	270	9	10
IC-1 ^b	59	87	100	48	68	76	30	30
IC-2 ^b	165	130	188	86	99	97	7	17

^aMeasurements conducted with 7.6 cm x 7.6 cm x 0.16 cm specimens in vertical orientation. Imposed energy flux in the center of the samples 2.5 watts/cm².

^bIntumescent coating on an aluminum substrate, whose dimensions were 7.6 cm x 7.6 cm x 0.042 cm.

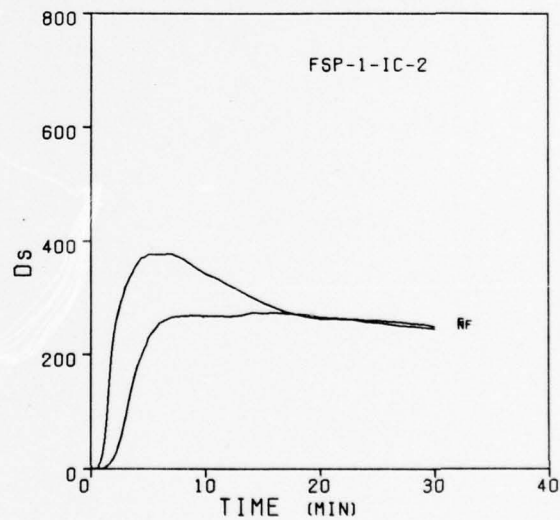
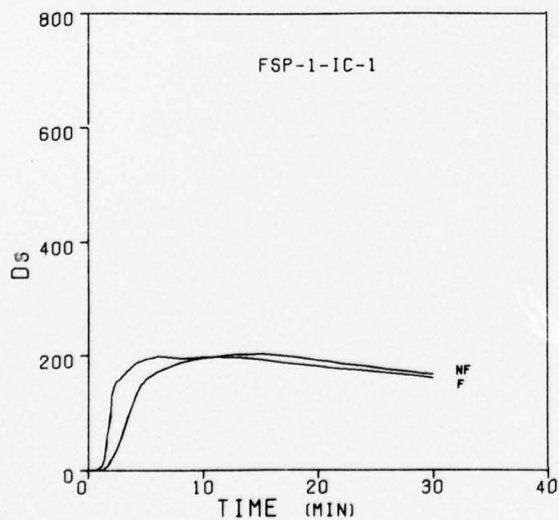
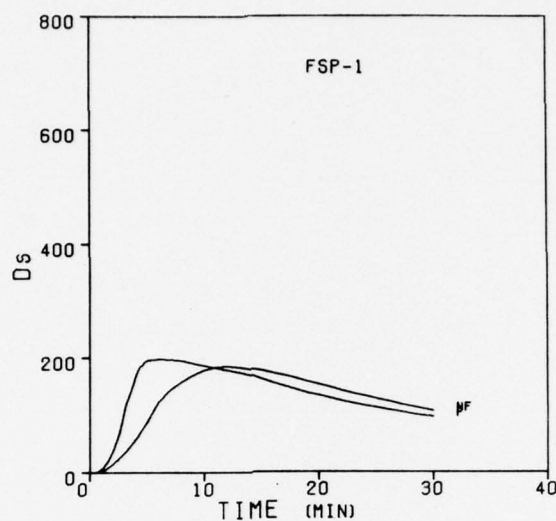


Figure 2. Smoke Optical Densities During the Burning of FSP-1-IC Compositions

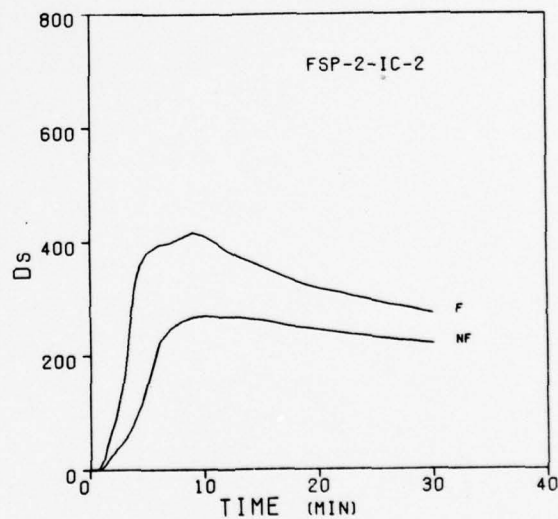
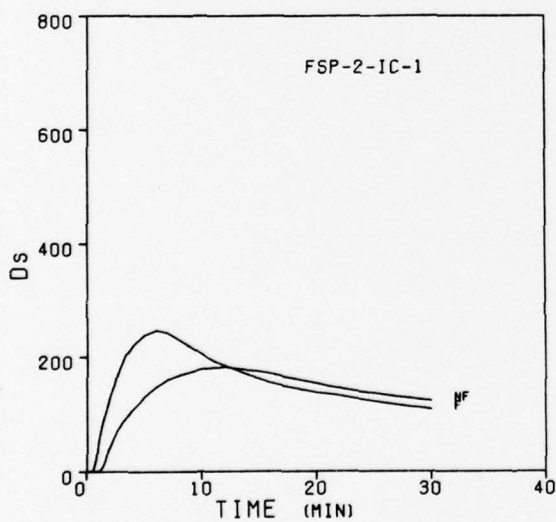
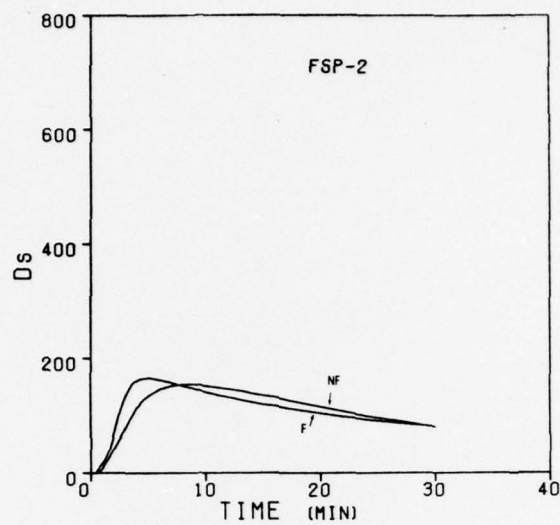


Figure 3. Smoke Optical Densities During the Burning of FSP-2-IC Compositions

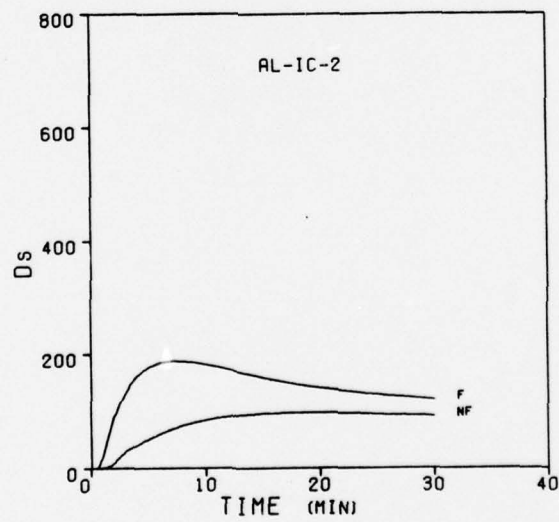
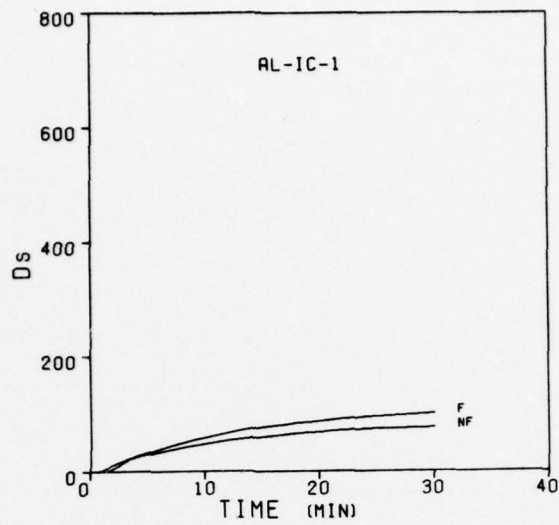


Figure 4. Smoke Optical Densities During the Exposure of Al-IC Compositions

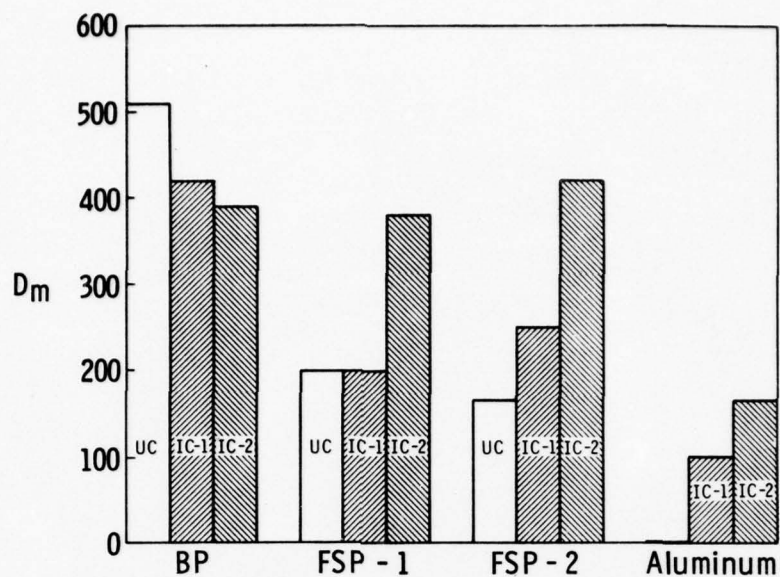


Figure 5. Maximum Specific Smoke Optical Densities Under Flame Exposure Conditions

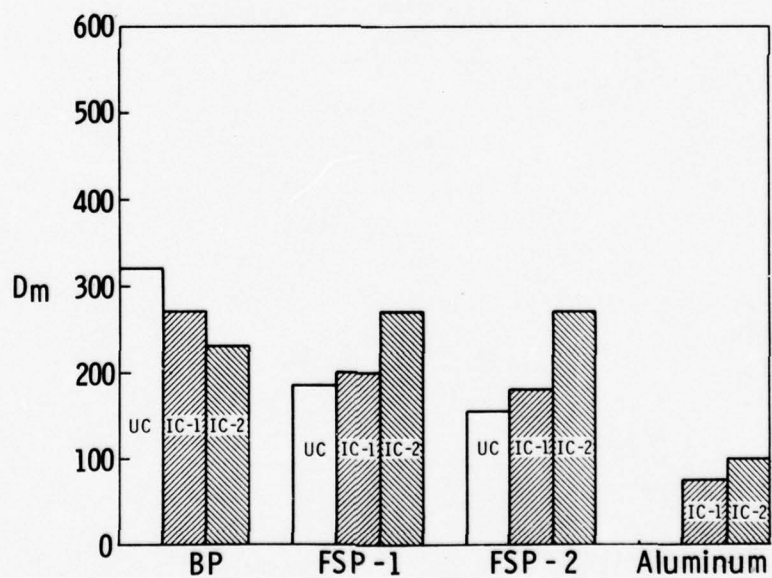


Figure 6. Maximum Specific Smoke Optical Densities Under Nonflame Exposure Conditions

Tests were subsequently conducted with thin aluminum sheet specimens that had been coated with intumescent paints. These tests demonstrated (see Figures 5 and 6) that the adverse effect, which was found to be especially pronounced with the epoxy-based material, indeed arose from smoke generated by the coating itself upon sustained exposure to the radiant energy source and to the flame.

The above results indicate need for intumescent coatings of very low propensity for smoke formation, to utilize fully the effectiveness of smoke-retardant additives incorporated into polymers. Some new candidate materials have recently been developed (Ref. 8). These merit experimental evaluation with the FSR PVC compositions developed in the present program.

With regard to the rates of smoke formation, it was generally found that they were reduced by the intumescent coatings.

3.2 FORMATION OF GASEOUS COMBUSTION PRODUCTS

The intumescent coatings reduced significantly the formation of carbon monoxide under nonflame exposure conditions (see Table II and Figures 7-9). This effect was especially noticeable with the FSP-1 composition.

The maximum concentrations of carbon monoxide formed under flame exposure conditions were not greatly affected by the coatings. However, it should be noted that significant carbon monoxide concentrations were generated under flame exposure conditions from the two intumescent coatings used in this work (see Figure 10). The formation of carbon monoxide from these coatings is attributed to the oxidation of the initially formed carbonaceous chars in the flame.

The formation of carbon dioxide from the FSP compositions was retarded by the intumescent coatings under the nonflame exposure conditions (see Table III).

The intumescent coatings enhanced slightly the formation of NO_x under both types of exposure conditions; however, they delayed the time when the maximum concentrations were reached. The epoxy coating enhanced NO_x formation more than the alkyd coating used in this work (see Table IV and Figures 15-18 in the Appendix).

The insulating coatings reduced the rate of hydrogen chloride formation, especially under nonflame exposure to the radiant energy source.

The feasibility of retaining the smoke-retardant characteristics of the FSP compositions, and enhancing other fire safety properties with recently developed intumescent compositions will be investigated in projected work.

Table II
SUMMARY OF CO CONCENTRATION DATA FOR SELECTED TIMES
FOR PVC COMPOSITIONS

Material	CO Concentration (ppm)						Time to Maximum CO Concentration (min)	
	Flame Exposure			Nonflame Exposure			Flame Exposure	Nonflame Exposure
	10 min	20 min	Max. Conc.	10 min	20 min	Max. Conc.		
BP	810	1450	1900	120	310	570	30	30
FSP-1	1190	1850	2200	170	960	1350	30	30
FSP-2	1030	1700	2100	220	700	850	30	30
BP-IC-1	910	1400	1850	50	153	230	30	30
BP-IC-2	700	1400	2000	23	92	180	30	30
FSP-1-IC-1	780	1700	2350	21	76	135	30	30
FSP-1-IC-2	880	1450	2050	35	125	210	30	30
FSP-2-IC-1	750	1300	1600	36	141	235	30	30
FSP-2-IC-2	590	1300	1950	32	115	200	30	30
IC-1	185	550	1400	3	12	25	30	30
IC-2	185	350	520	6	13	20	30	30

Table III
SUMMARY OF CO₂ CONCENTRATION DATA FOR SELECTED TIMES
FOR PVC COMPOSITIONS

Material	CO ₂ Concentration (%)						Time to Maximum CO ₂ Concentration (min)	
	Flame Exposure			Nonflame Exposure			Flame Exposure	Nonflame Exposure
	10 min	20 min	Max. Conc.	10 min	20 min	Max. Conc.		
BP	0.68	1.24	1.78	0.02	0.06	0.12	30	30
FSP-1	0.79	1.40	1.89	0.18	0.45	0.60	30	29
FSP-2	0.98	1.61	2.16	0.17	0.40	0.50	30	29
BP-IC-1	0.80	1.46	2.16	0.00	0.00	0.03	30	30
BP-IC-2	0.54	1.12	1.68	0.01	0.03	0.04	30	30
FSP-1-IC-1	0.79	1.11	1.40	0.07	0.13	0.16	30	30
FSP-1-IC-2	0.94	1.34	1.77	0.10	0.18	0.22	30	30
FSP-2-IC-1	1.00	1.67	2.32	0.11	0.16	0.20	30	30
FSP-2-IC-2	0.78	1.31	1.78	0.09	0.18	0.22	30	30
IC-1	0.44	0.75	1.05	0.02	0.02	0.03	30	30
IC-2	0.40	0.86	1.24	0.02	0.03	0.04	30	30

Table IV
SUMMARY OF NO_x CONCENTRATION DATA FOR SELECTED TIMES
FOR PVC COMPOSITIONS

Material	NO _x Concentration (ppm)						Time to Maximum NO _x Concentration (min)	
	Flame Exposure			Nonflame Exposure			Flame Exposure	Nonflame Exposure
	10 min	20 min	Max. Conc.	10 min	20 min	Max. Conc.		
BP	13	9.4	19	2.9	2.2	4.6	5	4
FSP-1	2.5	2.8	3.3	1.5	1.4	1.8	30	5
FSP-2	5.9	5.3	7.7	1.5	1.4	1.6	5	4
BP-IC-1	27	35	40	3.6	7.9	12	30	30
BP-IC-2	21	36	46	11	12	16	30	30
FSP-1-IC-1	33	35	37	3.6	8.4	13	30	30
FSP-1-IC-2	42	49	54	5.0	11	16	30	30
FSP-2-IC-1	22	28	31	2.9	6.2	9.1	30	30
FSP-2-IC-2	33	50	60	5.0	11	16	30	30
IC-1	16	19	21	2.2	4.0	6.0	30	30
IC-2	24	38	46	6.1	7.9	9.5	30	30

Table V

SUMMARY OF HYDROCARBONS CONCENTRATION DATA FOR SELECTED TIMES
FOR PVC COMPOSITIONS

Material	Hydrocarbons Concentration (ppm) ^a						Time to Maximum Hydrocarbons Concentration (min)	
	Flame Exposure			Nonflame Exposure			Flame Exposure	Nonflame Exposure
	10 min	20 min	Max. Conc.	10 min	20 min	Max. Conc.		
BP	4300	4600	5200	2800	2900	3000	30	17
FSP-1	2300	3000	3500	3400	3400	3500	30	13
FSP-2	2400	2600	2800	2900	2700	2900	30	14
BP-IC-1	4300	4400	4500	2600	3000	3000	24	19
BP-IC-2	5200	6200	6700	2200	3100	3100	30	20
FSP-1-IC-1	3700	5600	7100	1600	2500	2500	30	22
FSP-1-IC-2	3400	5500	7600	2500	3200	3200	30	18
FSP-2-IC-1	4200	4500	5000	3200	3300	3300	30	19
FSP-2-IC-2	3700	4500	5000	2100	3300	3400	29	21
IC-1	540	1750	2600	39	55	62	30	29
IC-2	660	800	830	310	360	360	25	20

^aDetermined by flame ionization measurement. Expressed in terms of methane equivalents.

Table VI

SUMMARY OF HCl CONCENTRATION DATA FOR SELECTED TIME
FOR PVC COMPOSITIONS

<u>Material</u>	<u>HCl Concentration (ppm)</u>					
	<u>Flame Exposure</u>			<u>Nonflame Exposure</u>		
	<u>5 min</u>	<u>15 min</u>	<u>30 min</u>	<u>5 min</u>	<u>15 min</u>	<u>30 min</u>
BP	1950	2400	1050	1900	2600	2200
FSP-1	1900	2200	1500	1650	2400	2100
FSP-2	1350	900	490	1500	2300	1900
BP-IC-1	2100	1250	620	1650	1850	1900
BP-IC-2	1200	2200	1150	520	1750	1850
FSP-1-IC-1	1250	1950	1400	(160)	950	1300
FSP-1-IC-2	900	1100	910	(250)	(330)	(<63)
FSP-2-IC-1	1250	780	940	(78)	1200	1600
FSP-2-IC-2	(120)	(190)	(140)	220	1000	1000
IC-1						
IC-2	<63	<63	<63	<63	<63	<63

4. ACKNOWLEDGMENT

The authors are indebted to Mr. R. D. Myers for the compounding and molding of the PVC compositions. They also wish to express appreciation to Miss K. A. Flayler, Mr. J. T. Miller and Mr. N. F. May for computerized data processing.

5. REFERENCES

1. L. Parts and C. A. Thompson, "Flame- and Smoke-Retardant Polymer Systems," First Quarterly Report on Contract N00024-76-C-5336, 15 September 1976.
2. Sales Merchandising Bulletin No. 1403, "Intumescent Fire Retardant Paint," C. M. Athey Paint Company.
3. Product Information Bulletin "Ocean Intumescent Fire Retardant Catalytic Epoxy Paint No. 477," Ocean Chemicals, Inc.
4. L. Parts, R. G. Olt and G. W. Wooten, "Products Resulting From Polymer Combustion," Polymer Conference Series, Flammability of Materials, University of Utah, Salt Lake City, Utah, July 11, 1974.
5. J. A. Ellard, "Performance of Intumescent Fire Barriers," presented at the 165th National Meeting of the American Chemical Society, Dallas, Texas, April 1973.
6. J. T. Miller and L. Parts, "Enhancement of Fire Performance of Fiberglass-Reinforced Plastic Panels by Fire-Retardant Coatings," MRC Report MRC-DA-456, November 1974.
7. R. Slysh, "Flame-Retardant Coatings for Plastics," *J. Paint Technol.* 47, 31 (1975).
8. Personal communication from E. Goldsmith, Ocean Chemicals, Inc., 20 April 1977.

APPENDIX

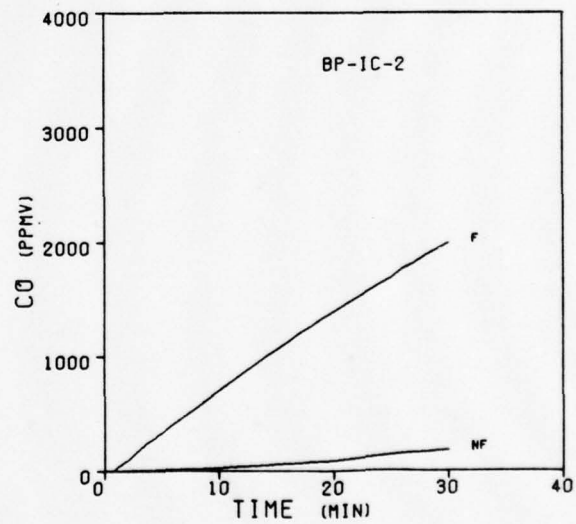
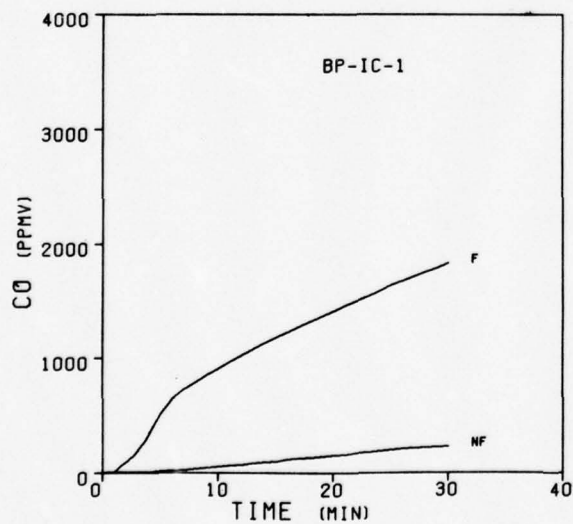
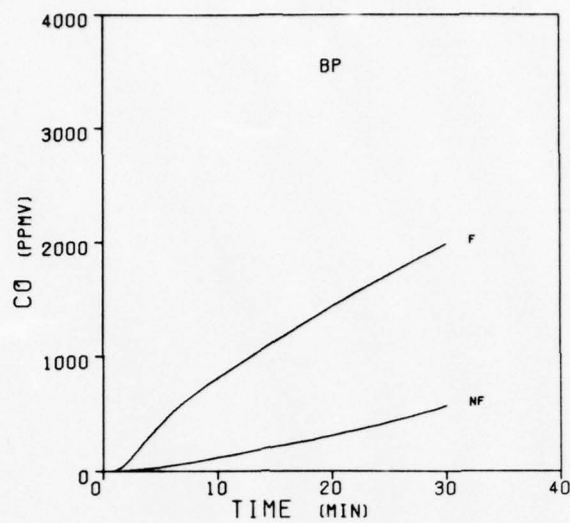


Figure 7. Carbon Monoxide Concentrations During the Burning of BP-IC Compositions

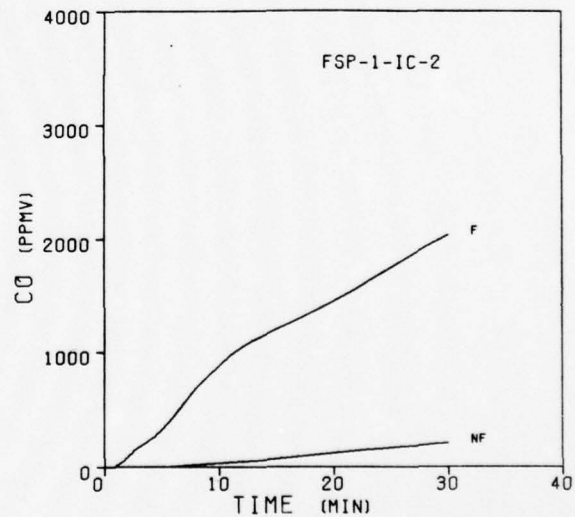
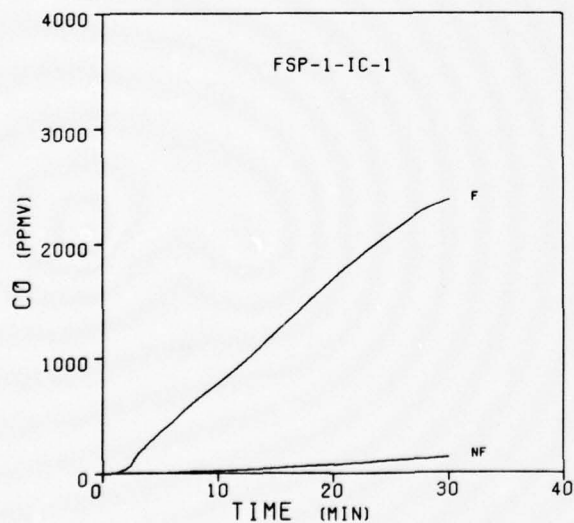
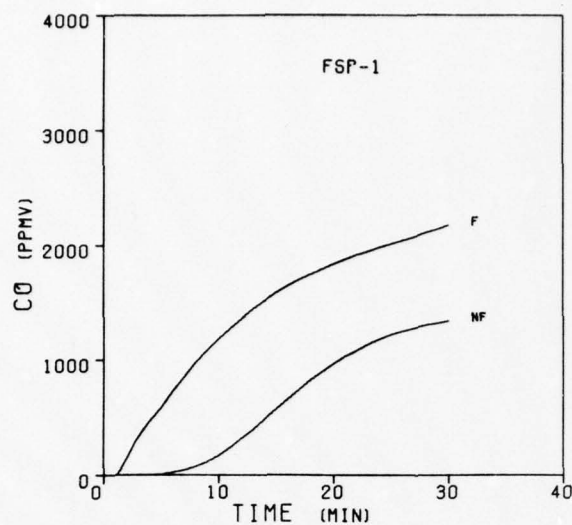


Figure 8. Carbon Monoxide Concentrations During the Burning of FSP-1-IC Compositions

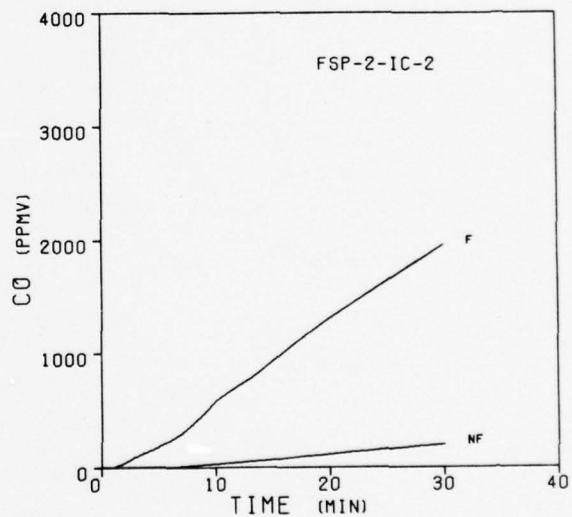
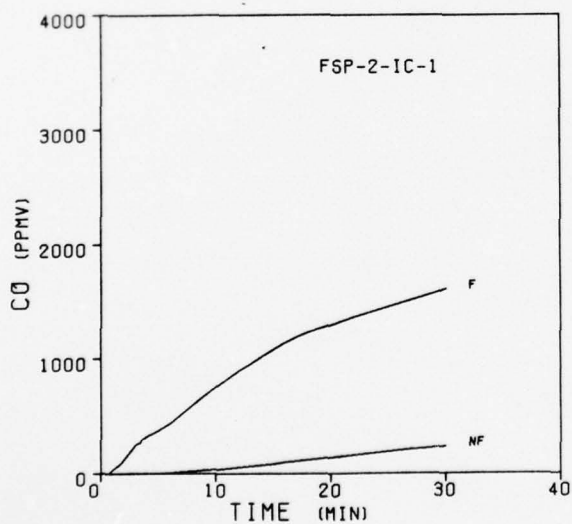
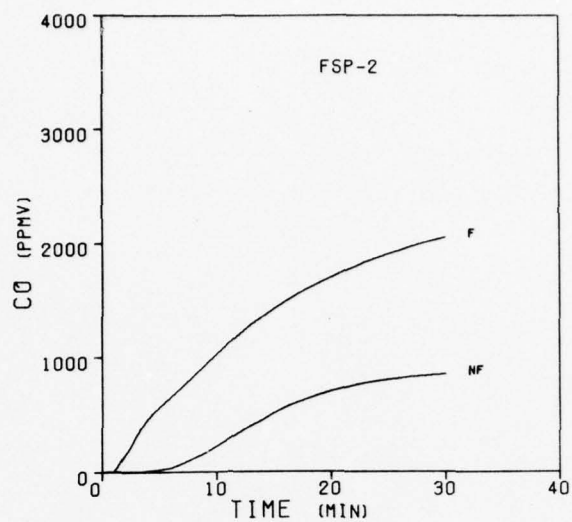


Figure 9. Carbon Monoxide Concentrations During the Burning of FSP-2-IC Compositions

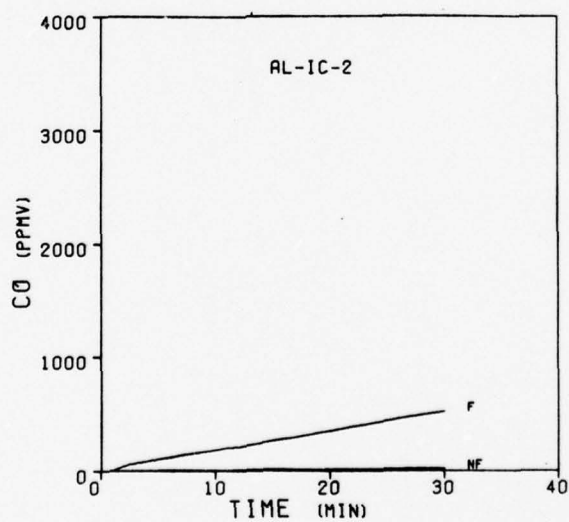
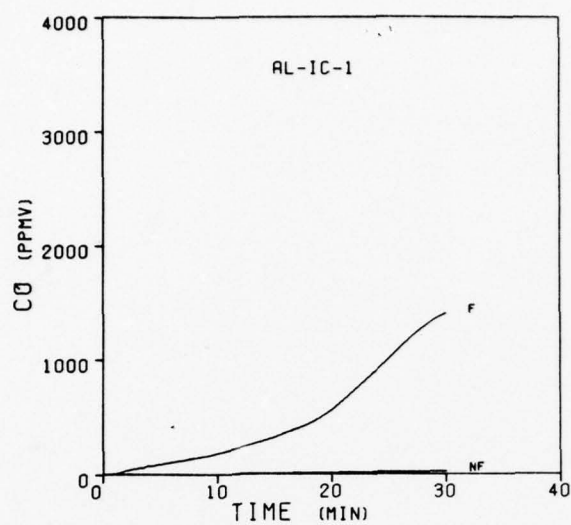


Figure 10. Carbon Monoxide Concentrations During the Exposure of Al-IC Compositions

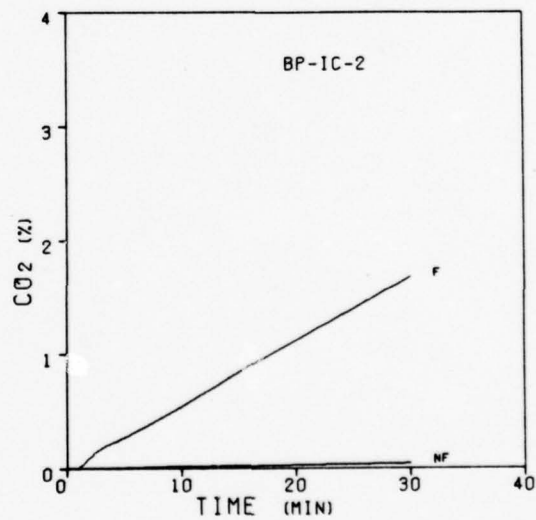
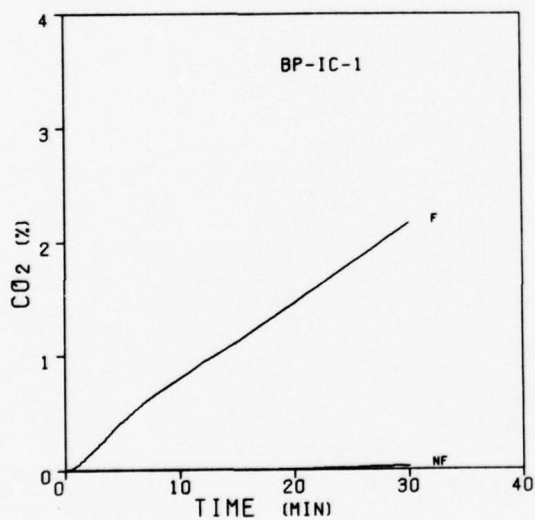
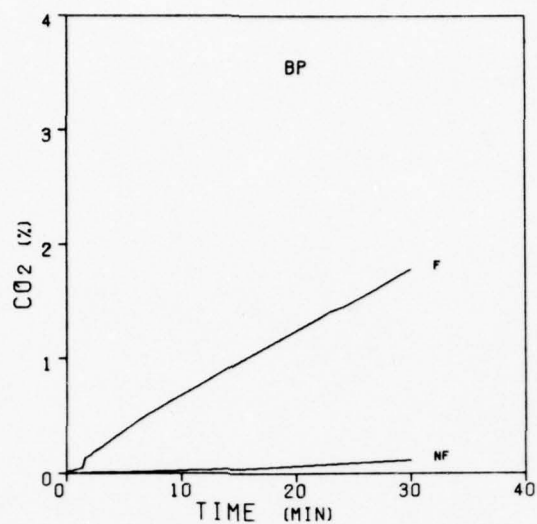


Figure 11. Carbon Dioxide Concentrations During the Burning of BP-IC Compositions

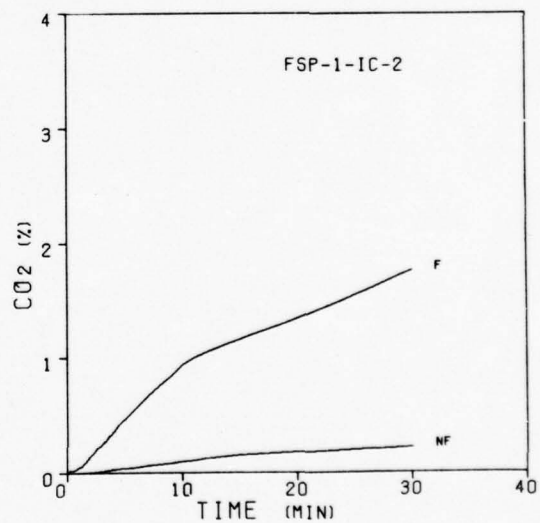
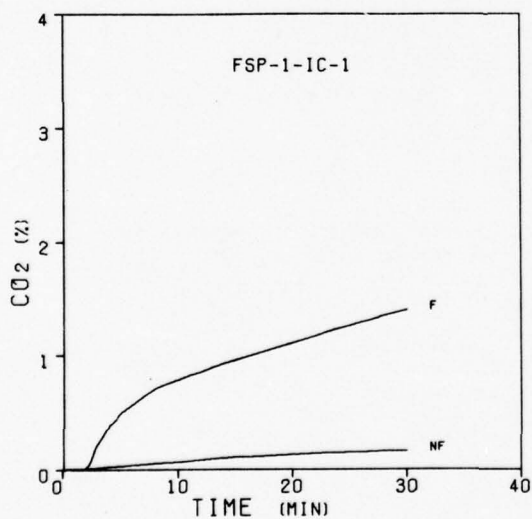
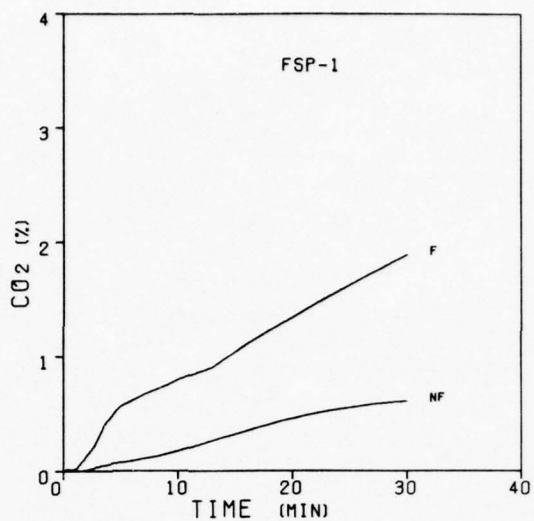


Figure 12. Carbon Dioxide Concentrations During the Burning of FSP-1-IC Compositions

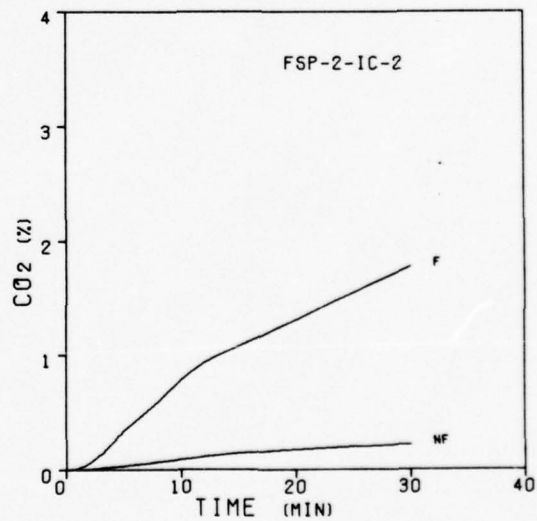
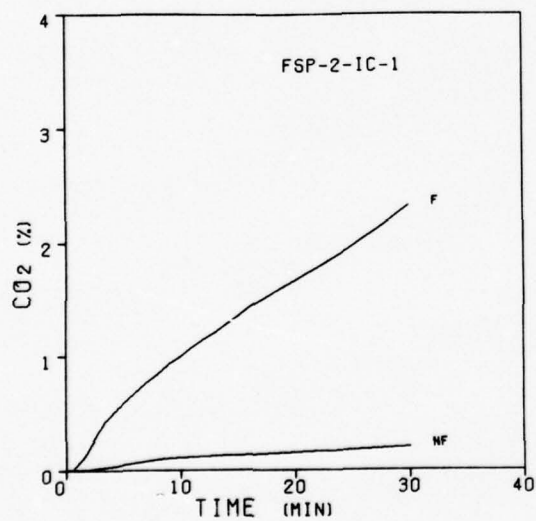
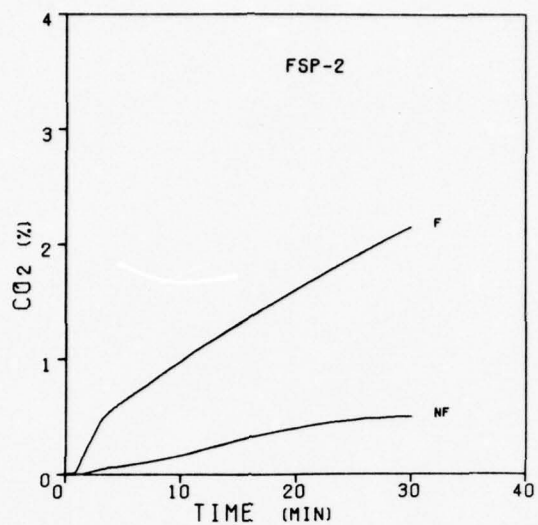


Figure 13. Carbon Dioxide Concentrations During the Burning of FSP-2-IC Compositions

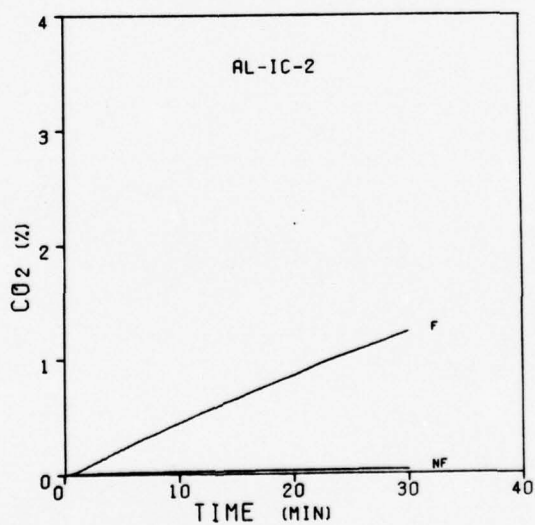
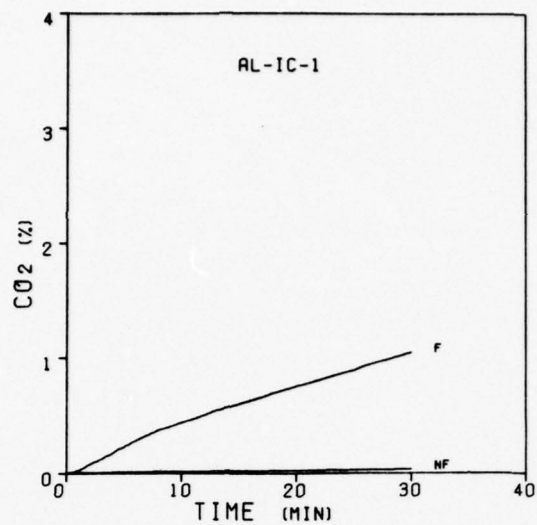


Figure 14. Carbon Dioxide Concentrations During the Exposure of Al-IC Compositions

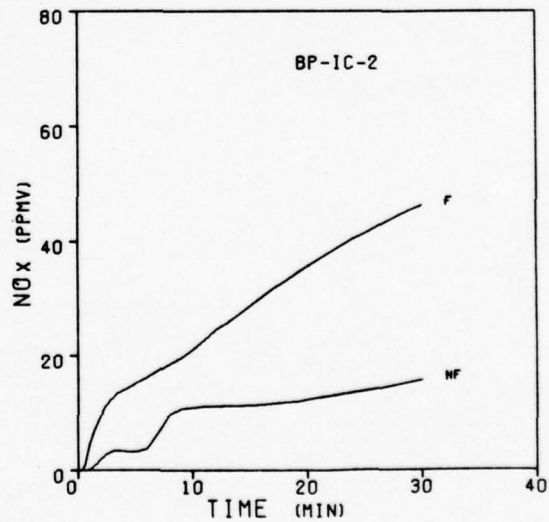
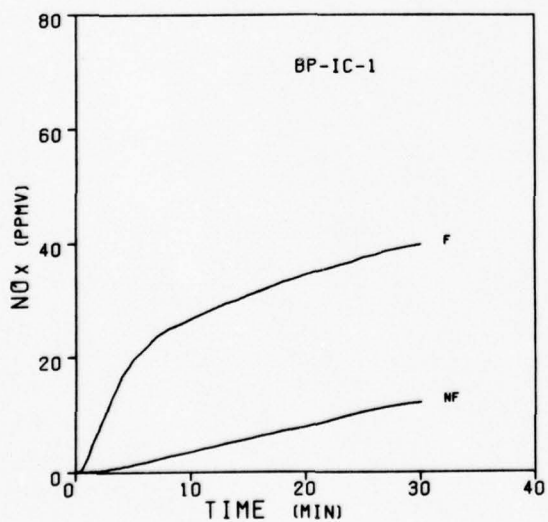
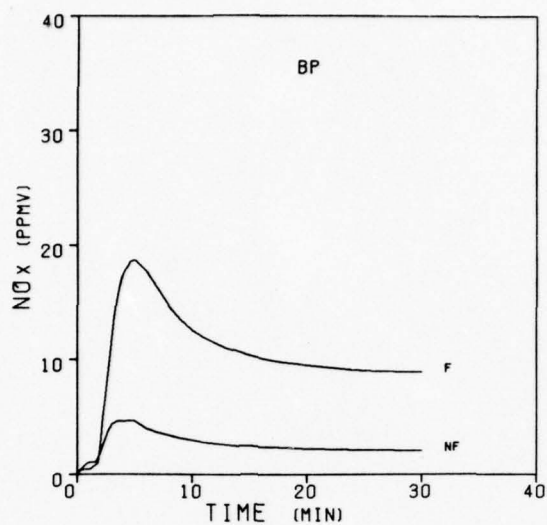


Figure 15. NO_x Concentrations During the Burning of BP-IC Compositions

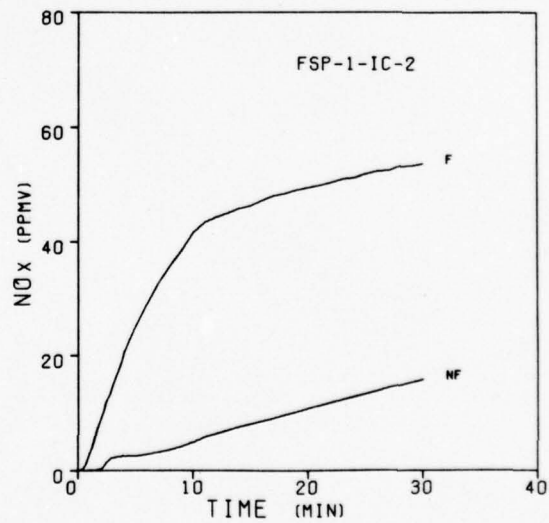
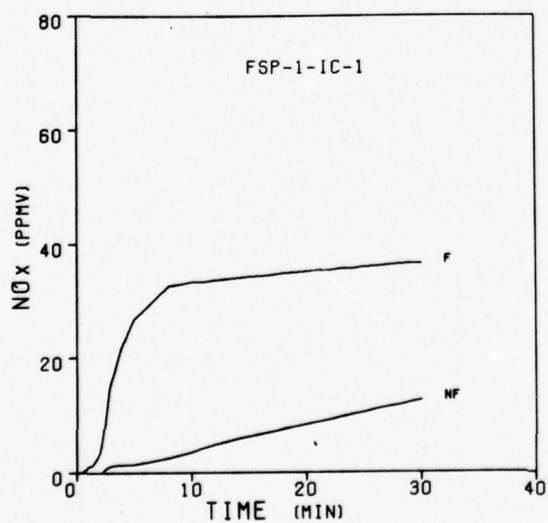
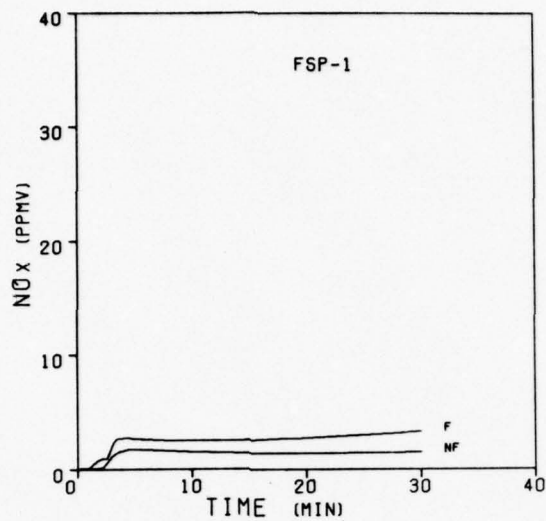


Figure 16. NO_x Concentrations During the Burning of FSP-1-IC Compositions

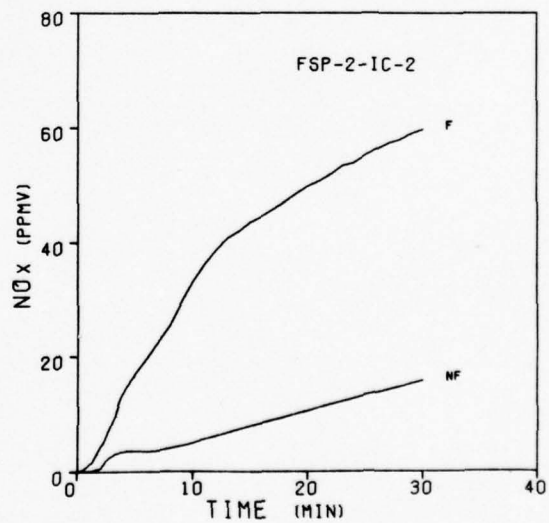
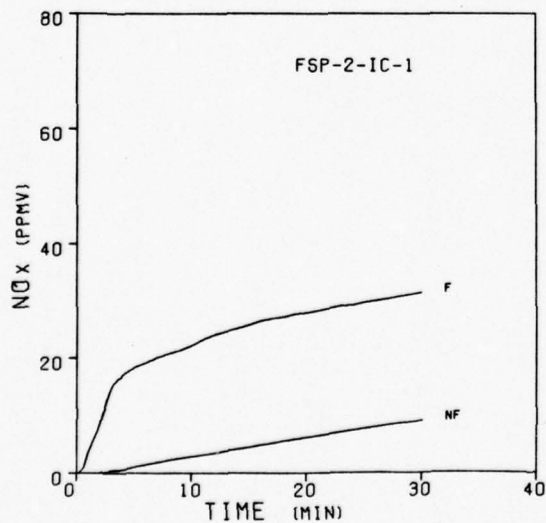
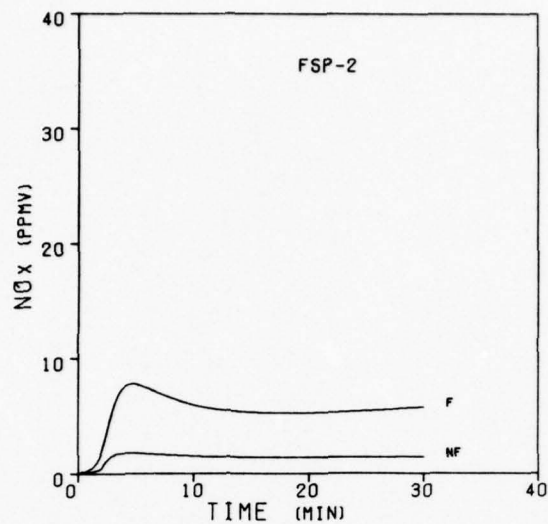


Figure 17. NO_x Concentrations During the Burning of FSP-2-IC Compositions

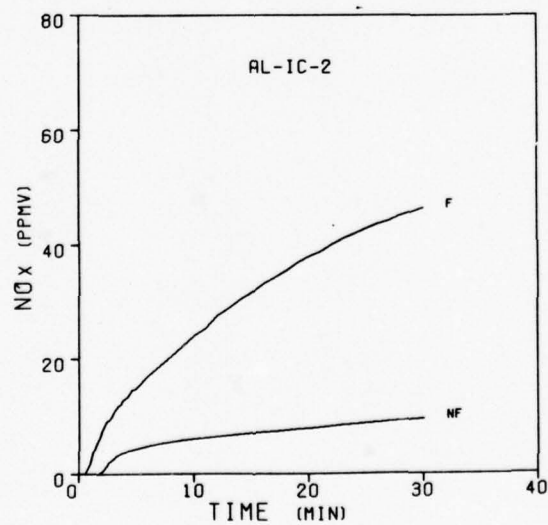
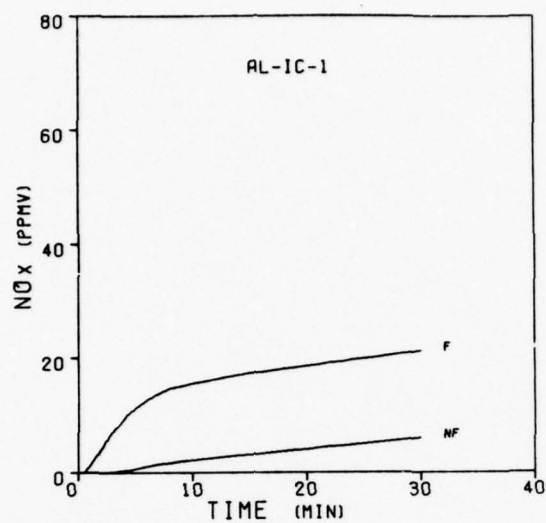


Figure 18. NO_x Concentrations during the Exposure of Al-IC Compositions

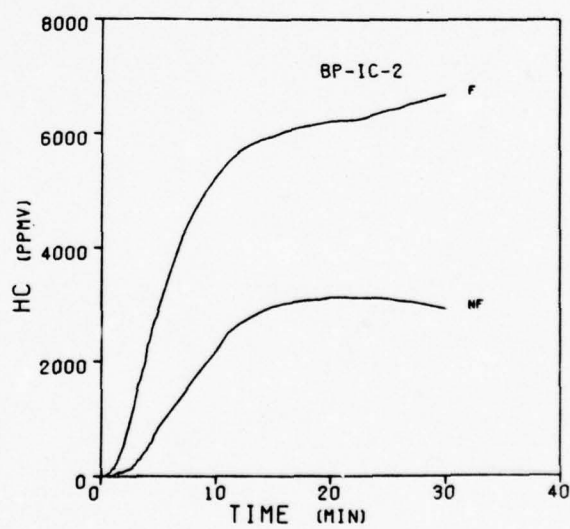
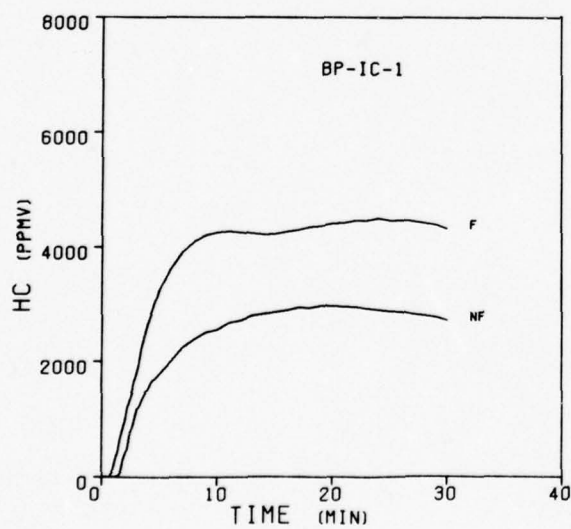
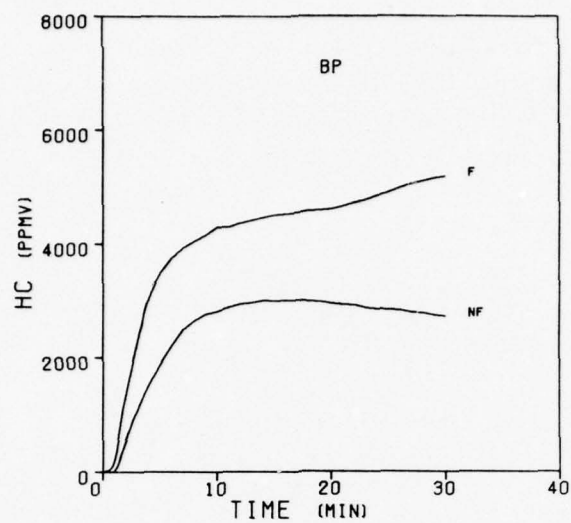


Figure 19. Hydrocarbons Concentrations During the Burning of BP Compositions

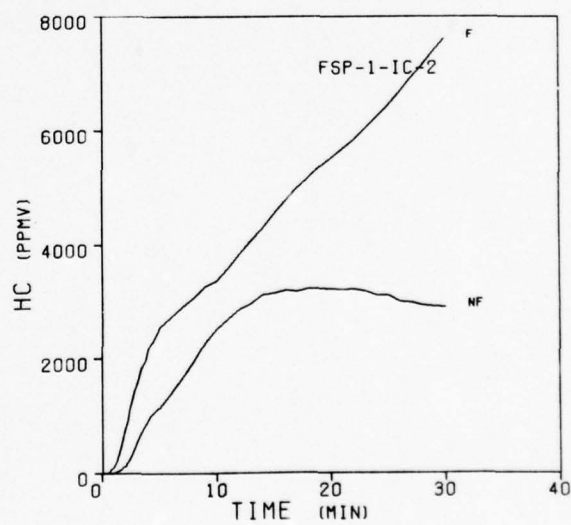
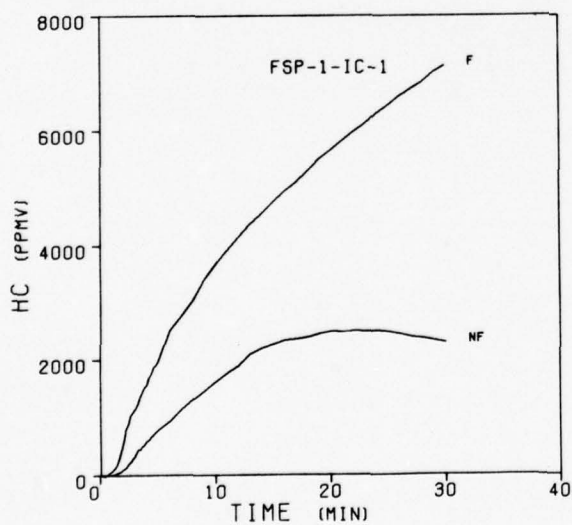
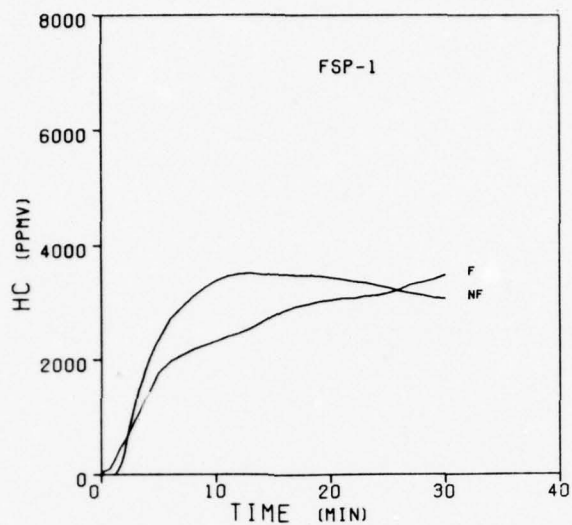


Figure 20. Hydrocarbons Concentrations During the Burning of FSP-1-IC Compositions

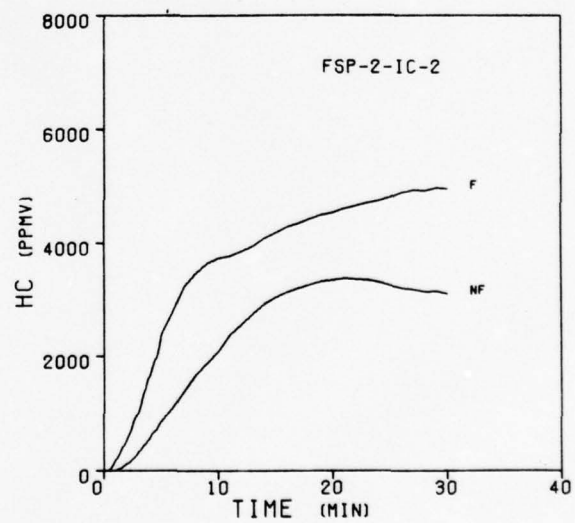
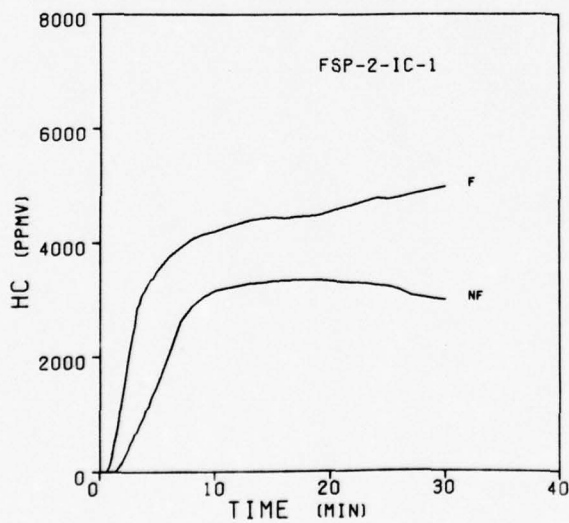
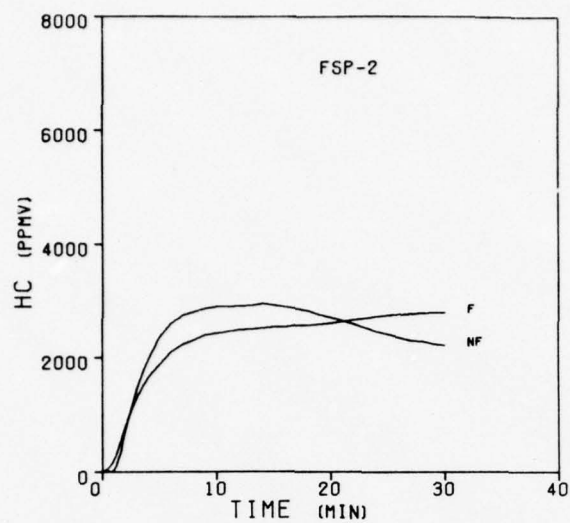


Figure 21. Hydrocarbons Concentrations During the Burning of FSP-2-IC Compositions

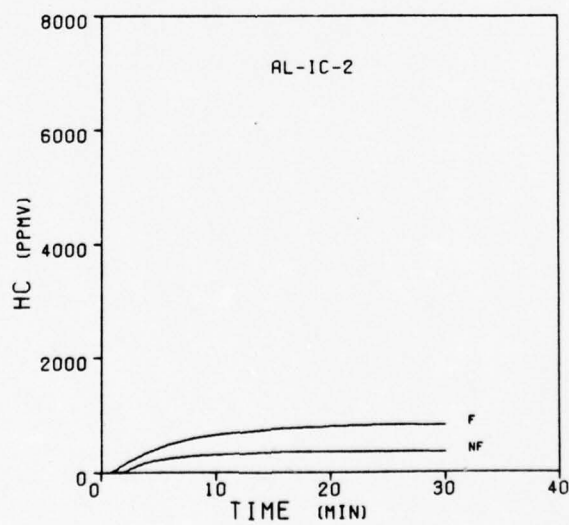
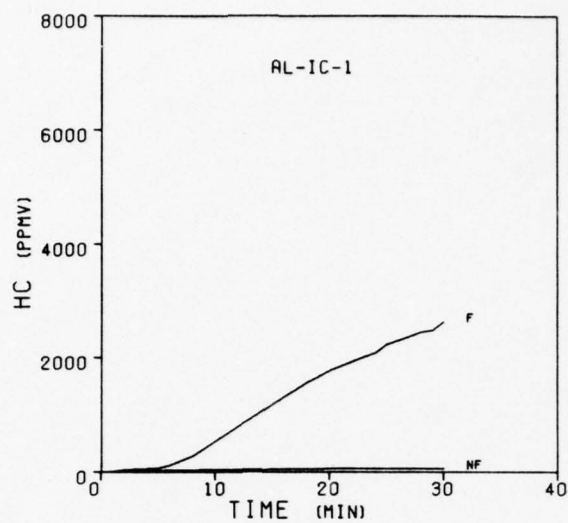


Figure 22. Hydrocarbons Concentrations During the Exposure of Al-IC Compositions

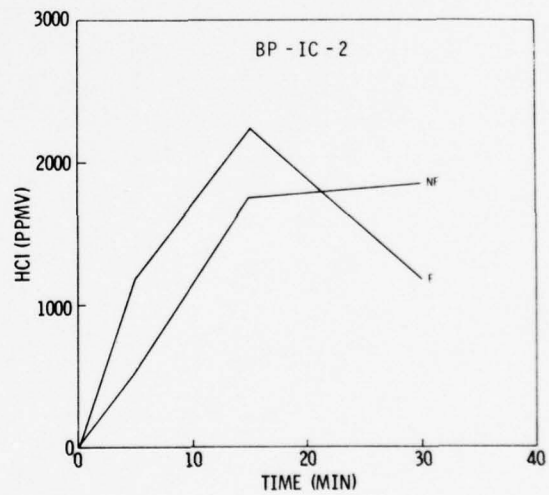
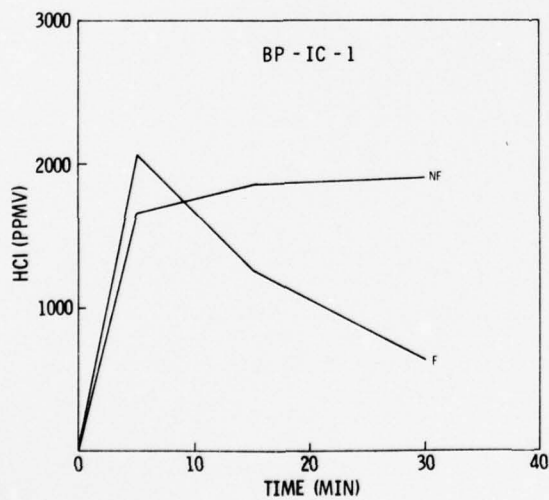
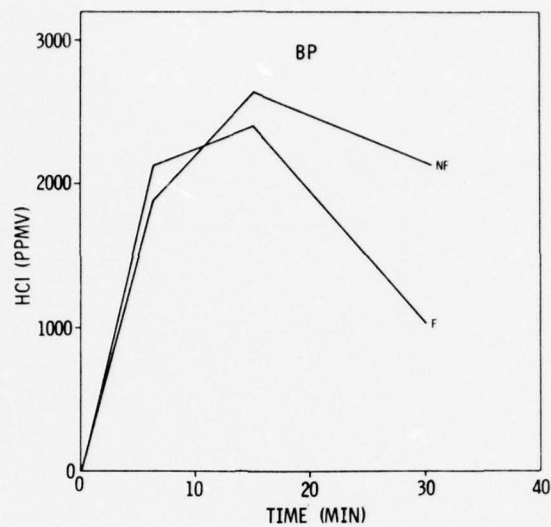


Figure 23. HCl Concentrations During the Burning of BP Compositions

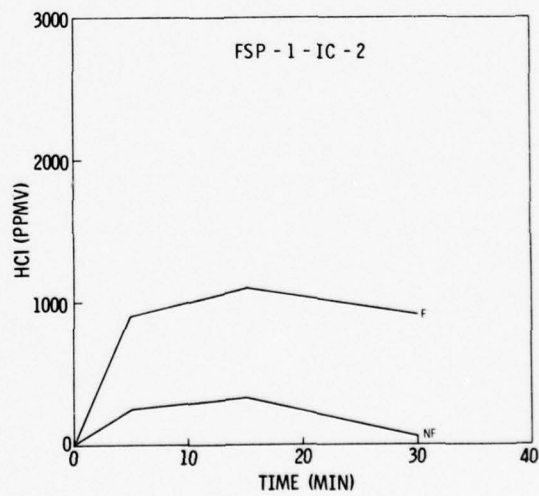
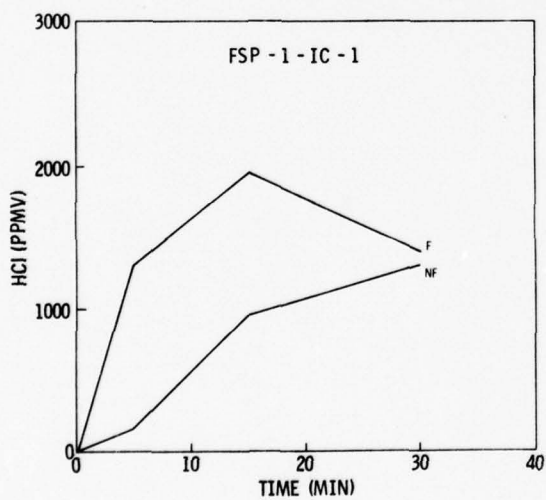
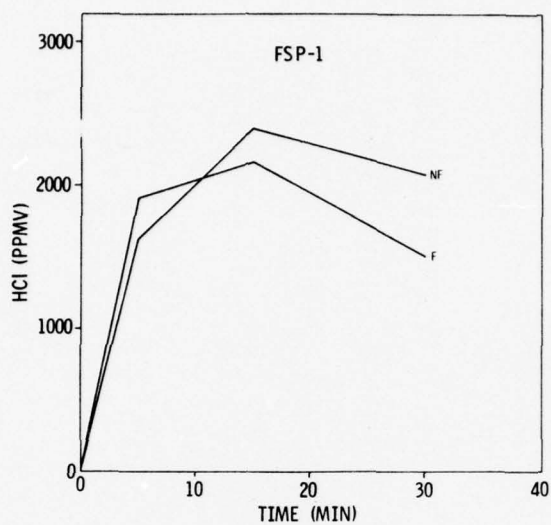


Figure 24. HCl Concentrations During the Burning of FSP-1-IC Compositions

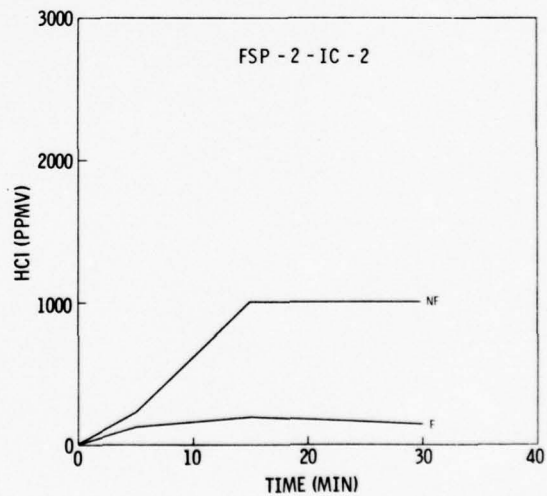
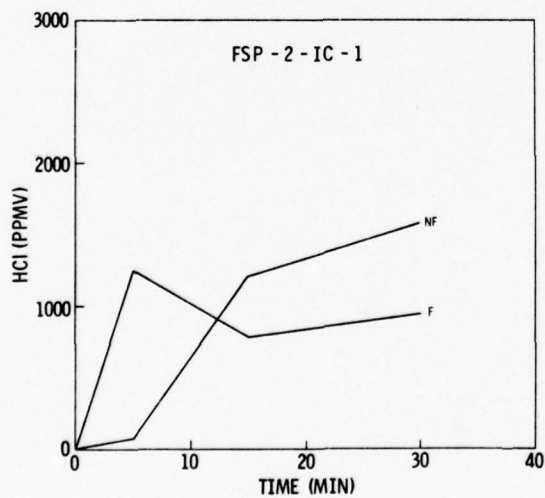
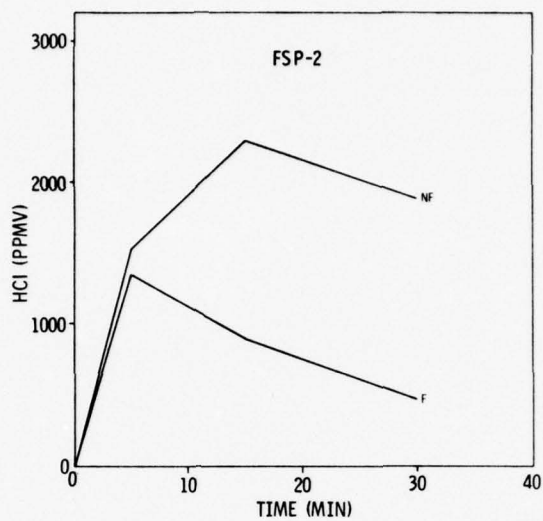


Figure 25. HCl Concentrations During the Burning of FSP-2-IC Compositions

Table VII
SAMPLE MASS DATA

<u>Material</u>	<u>Sample Mass (g)^a</u>		<u>Consumed Mass (g)^b</u>	
	<u>Flame Exposure</u>	<u>Nonflame Exposure</u>	<u>Flame Exposure</u>	<u>Nonflame Exposure</u>
BP-IC-1	11.58	12.82		7.26
BP-IC-2	12.55	12.82		
FSP-1-IC-1	17.56	16.98		5.95
FSP-1-IC-2	15.68	17.57		7.13
FSP-2-IC-1	13.24	15.43	6.63	6.00
FSP-2-IC-2	16.96	16.07	7.55	7.42
Al-IC-1	9.10	9.19		
Al-IC-2	8.50	8.44	1.51	0.86

^aThe dimensions of plastic specimens were 7.6 cm x 7.6 cm x 0.16 cm. The dimensions of the coated aluminum specimens were 7.6 cm x 7.6 cm x 0.066 cm.

^bThe chars formed from some specimens could not be recovered completely. Therefore, the data in the consumed mass column are incomplete.

Table VIII

COMBUSTION PRODUCTS FORMED FROM BP-IC-1
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL PVC-BP-IC-1
 SAMPLE MASS AVG 11.5759
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	66.	11.	0.04	149.	2.3	21.00
2.	204.	97.	0.13	968.	7.2	20.92
3.	277.	189.	0.23	1768.	12.3	20.71
4.	343.	266.	0.33	2668.	16.8	20.67
5.	399.	514.	0.43	3258.	19.7	20.44
6.	418.	646.	0.52	3631.	21.6	20.36
7.	424.	727.	0.60	3916.	23.7	20.22
8.	417.	786.	0.67	4105.	25.0	19.99
9.	399.	849.	0.74	4210.	25.8	19.94
10.	383.	907.	0.80	4263.	26.8	19.86
11.	363.	967.	0.87	4278.	27.7	19.75
12.	346.	1021.	0.94	4256.	28.6	19.64
13.	332.	1075.	1.00	4241.	29.5	19.52
14.	320.	1130.	1.06	4218.	30.1	19.35
15.	307.	1180.	1.12	4233.	31.0	19.31
16.	301.	1227.	1.19	4271.	31.7	19.26
17.	295.	1274.	1.26	4301.	32.5	19.14
18.	291.	1320.	1.32	4346.	33.3	19.00
19.	287.	1365.	1.39	4369.	33.9	18.88
20.	283.	1411.	1.46	4407.	34.6	18.72
21.	279.	1458.	1.54	4422.	35.2	18.62
22.	273.	1499.	1.60	4459.	35.7	18.52
23.	269.	1542.	1.67	4459.	36.3	18.40
24.	265.	1586.	1.74	4497.	36.8	18.29
25.	258.	1640.	1.82	4459.	37.6	18.20
26.	251.	1676.	1.88	4475.	38.0	18.05
27.	246.	1717.	1.95	4452.	38.7	17.93
28.	239.	1753.	2.02	4422.	39.1	17.78
29.	232.	1789.	2.09	4392.	39.5	17.71
30.	226.	1837.	2.16	4324.	39.8	17.59

Table IX

COMBUSTION PRODUCTS FORMED FROM BP-IC-1
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-BP-IC-1
 SAMPLE MASS AVG 12.8166
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	1.	4.	0.00	12.	0.1	20.87
2.	98.	4.	0.00	411.	0.3	20.70
3.	189.	4.	0.00	1181.	0.7	20.80
4.	225.	6.	0.00	1509.	1.0	20.66
5.	248.	13.	0.00	1794.	1.4	20.79
6.	260.	19.	0.00	2006.	1.8	20.68
7.	268.	27.	0.00	2245.	2.3	20.66
8.	272.	36.	0.00	2393.	2.8	20.62
9.	271.	45.	0.00	2511.	3.2	20.60
10.	271.	53.	0.00	2562.	3.6	20.55
11.	270.	65.	0.00	2679.	4.1	20.55
12.	268.	72.	0.00	2724.	4.5	20.44
13.	264.	87.	0.00	2801.	5.0	20.39
14.	259.	96.	0.00	2825.	5.4	20.32
15.	254.	102.	0.00	2864.	5.8	20.21
16.	249.	119.	0.00	2885.	6.3	20.29
17.	243.	128.	0.00	2940.	6.7	20.11
18.	238.	137.	0.00	2934.	7.2	20.17
19.	234.	144.	0.00	2965.	7.5	20.20
20.	229.	156.	0.00	2961.	7.9	20.20
21.	224.	161.	0.01	2947.	8.4	20.20
22.	220.	174.	0.01	2944.	8.9	20.19
23.	216.	182.	0.01	2911.	9.5	20.17
24.	211.	191.	0.01	2894.	10.0	20.16
25.	207.	199.	0.02	2872.	10.5	20.15
26.	202.	208.	0.02	2858.	10.9	20.14
27.	198.	215.	0.02	2816.	11.3	20.14
28.	194.	222.	0.03	2801.	11.6	20.13
29.	189.	224.	0.03	2768.	11.9	20.13
30.	185.	232.	0.03	2715.	12.1	20.13

Table X

COMBUSTION PRODUCTS FORMED FROM BP-IC-2
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL PVC-BP-IC-2
 SAMPLE MASS AVG 12.5466
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	29.	24.	0.00	136.	4.6	21.00
2.	167.	97.	0.10	567.	9.4	20.84
3.	236.	187.	0.18	1399.	12.6	20.70
4.	268.	266.	0.23	2283.	14.1	20.59
5.	284.	337.	0.27	2954.	15.2	20.51
6.	300.	411.	0.32	3589.	16.2	20.51
7.	316.	481.	0.38	4187.	17.4	20.45
8.	331.	548.	0.43	4611.	18.5	20.24
9.	346.	624.	0.48	4966.	19.6	20.21
10.	363.	699.	0.54	5245.	21.0	20.04
11.	379.	772.	0.60	5502.	22.7	20.00
12.	386.	845.	0.66	5690.	24.5	19.96
13.	383.	916.	0.71	5811.	25.7	19.79
14.	375.	988.	0.78	5902.	27.2	19.79
15.	367.	1054.	0.84	5962.	28.7	19.69
16.	356.	1126.	0.90	6038.	30.2	19.57
17.	350.	1198.	0.96	6098.	31.7	19.43
18.	340.	1261.	1.01	6136.	32.9	19.47
19.	333.	1332.	1.07	6181.	34.3	19.42
20.	325.	1390.	1.12	6219.	35.6	19.34
21.	318.	1453.	1.18	6226.	36.8	19.29
22.	311.	1515.	1.23	6241.	38.0	19.27
23.	304.	1575.	1.29	6279.	39.2	19.21
24.	298.	1634.	1.34	6355.	40.4	19.12
25.	291.	1689.	1.40	6407.	41.3	19.01
26.	285.	1770.	1.45	6453.	42.4	18.87
27.	279.	1819.	1.51	6528.	43.5	18.75
28.	274.	1887.	1.57	6581.	44.5	18.63
29.	268.	1942.	1.62	6641.	45.4	18.53
30.	263.	1993.	1.68	6694.	46.2	18.38

Table XI

COMBUSTION PRODUCTS FORMED FROM BP-IC-2
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-BP-IC-2
 SAMPLE MASS AVG 12.8162
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME(MIN)	DS	CO(PPMV)	CO ₂ (%)	HC(PPMV)	NOX(PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	6.	2.	0.00	10.	0.2	20.82
2.	32.	2.	0.00	90.	2.1	20.79
3.	58.	5.	0.00	220.	3.4	20.81
4.	150.	7.	0.00	472.	3.3	20.79
5.	193.	9.	0.00	858.	3.2	20.70
6.	209.	10.	0.00	1129.	3.8	20.68
7.	216.	14.	0.01	1392.	6.6	20.70
8.	222.	15.	0.01	1680.	9.8	20.77
9.	224.	19.	0.01	1942.	10.7	20.75
10.	227.	23.	0.01	2180.	10.9	20.79
11.	227.	35.	0.01	2495.	11.1	20.70
12.	227.	38.	0.02	2662.	11.1	20.85
13.	228.	45.	0.02	2782.	11.2	20.81
14.	227.	52.	0.02	2888.	11.2	20.89
15.	225.	60.	0.02	2971.	11.3	20.75
16.	226.	66.	0.02	3024.	11.4	20.74
17.	223.	72.	0.02	3046.	11.6	20.74
18.	220.	82.	0.03	3077.	11.8	20.68
19.	219.	87.	0.03	3092.	11.9	20.71
20.	216.	92.	0.03	3129.	12.3	20.73
21.	214.	100.	0.03	3129.	12.6	20.70
22.	212.	110.	0.03	3122.	12.9	20.65
23.	211.	121.	0.03	3122.	13.2	20.58
24.	209.	131.	0.03	3107.	13.5	20.50
25.	208.	142.	0.03	3099.	13.8	20.44
26.	207.	151.	0.04	3062.	14.1	20.40
27.	206.	159.	0.04	3046.	14.5	20.37
28.	204.	166.	0.04	3009.	14.9	20.36
29.	202.	173.	0.04	2971.	15.3	20.36
30.	201.	180.	0.04	2926.	15.7	20.36

Table XII

COMBUSTION PRODUCTS FORMED FROM FSP-1-IC-1
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL FSP-1-IC-1
 SAMPLE MASS AVG 17.5614
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NO _x (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	5.	6.	0.00	79.	1.1	20.80
2.	127.	42.	0.02	592.	3.4	20.64
3.	165.	162.	0.23	1147.	16.0	20.54
4.	185.	265.	0.39	1556.	22.6	20.33
5.	194.	362.	0.50	1969.	26.9	20.18
6.	199.	441.	0.57	2515.	28.8	20.03
7.	197.	538.	0.64	2775.	30.8	19.92
8.	195.	627.	0.71	3045.	32.7	19.80
9.	196.	705.	0.75	3406.	33.0	19.75
10.	198.	778.	0.79	3679.	33.4	19.60
11.	198.	860.	0.82	3919.	33.4	19.56
12.	197.	946.	0.86	4150.	33.7	19.49
13.	197.	1035.	0.90	4369.	33.9	19.47
14.	195.	1128.	0.93	4551.	34.1	19.43
15.	193.	1223.	0.96	4748.	34.3	19.27
16.	190.	1319.	0.99	4944.	34.4	19.29
17.	187.	1409.	1.02	5095.	34.6	19.19
18.	185.	1505.	1.05	5276.	34.9	19.14
19.	183.	1597.	1.08	5502.	35.0	19.08
20.	181.	1688.	1.11	5646.	35.2	19.13
21.	178.	1778.	1.14	5812.	35.4	19.06
22.	176.	1857.	1.17	5970.	35.4	18.97
23.	175.	1941.	1.20	6114.	35.7	18.88
24.	173.	2014.	1.23	6295.	35.7	18.96
25.	171.	2091.	1.26	6431.	36.0	18.86
26.	169.	2162.	1.29	6589.	36.1	18.84
27.	167.	2236.	1.32	6718.	36.3	18.84
28.	165.	2206.	1.35	6838.	36.5	18.69
29.	163.	2286.	1.38	7012.	36.6	18.66
30.	160.	2373.	1.40	7133.	36.6	18.62

Table XIII

COMBUSTION PRODUCTS FORMED FROM FSP-1-IC-1
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-1-IC-1
 SAMPLE MASS AVG 16.9847
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NO _x (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	1.	0.	0.00	10.	0.0	20.85
2.	20.	0.	0.01	111.	0.0	20.85
3.	68.	0.	0.01	354.	1.2	20.81
4.	125.	0.	0.02	589.	1.4	20.82
5.	159.	2.	0.03	794.	1.5	20.78
6.	172.	6.	0.04	937.	1.8	20.78
7.	180.	10.	0.05	1140.	2.2	20.89
8.	188.	13.	0.05	1308.	2.6	20.89
9.	193.	17.	0.06	1464.	3.1	20.84
10.	196.	21.	0.07	1616.	3.6	20.81
11.	198.	25.	0.08	1767.	4.3	20.81
12.	201.	30.	0.09	1896.	4.9	20.84
13.	202.	35.	0.09	2105.	5.4	20.85
14.	202.	40.	0.10	2201.	5.9	20.76
15.	203.	46.	0.11	2271.	6.3	20.85
16.	201.	55.	0.11	2345.	6.7	20.71
17.	199.	59.	0.12	2364.	7.1	20.81
18.	197.	66.	0.12	2389.	7.6	20.63
19.	194.	70.	0.13	2446.	8.0	20.61
20.	191.	76.	0.13	2485.	8.4	20.67
21.	189.	83.	0.13	2482.	8.8	20.73
22.	185.	89.	0.14	2499.	9.2	20.65
23.	183.	96.	0.14	2494.	9.7	20.70
24.	181.	105.	0.15	2499.	10.1	20.69
25.	178.	109.	0.15	2482.	10.5	20.66
26.	175.	115.	0.15	2435.	11.0	20.67
27.	173.	122.	0.16	2392.	11.4	20.70
28.	171.	120.	0.16	2367.	11.7	20.69
29.	168.	128.	0.16	2325.	12.2	20.73
30.	167.	134.	0.16	2286.	12.6	20.70

Table XIV

COMBUSTION PRODUCTS FORMED FROM FSP-1-IC-2
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-1-IC-2
 SAMPLE MASS AVG 15.6842
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	23.	13.	0.05	105.	3.0	21.00
2.	234.	85.	0.14	783.	9.2	21.00
3.	319.	173.	0.25	1537.	14.8	20.96
4.	359.	239.	0.36	2149.	20.6	20.75
5.	377.	324.	0.47	2551.	25.2	20.63
6.	377.	437.	0.57	2732.	29.1	20.39
7.	378.	565.	0.67	2915.	32.8	20.27
8.	369.	691.	0.76	3069.	35.8	20.13
9.	355.	788.	0.84	3271.	38.5	19.98
10.	342.	884.	0.94	3372.	41.6	19.80
11.	334.	979.	1.00	3594.	43.4	19.67
12.	322.	1048.	1.05	3840.	44.3	19.58
13.	312.	1109.	1.09	4072.	45.0	19.51
14.	301.	1160.	1.12	4284.	45.8	19.44
15.	291.	1209.	1.16	4533.	46.3	19.46
16.	283.	1256.	1.20	4759.	47.2	19.33
17.	275.	1305.	1.23	4978.	48.0	19.20
18.	270.	1355.	1.27	5159.	48.4	19.13
19.	266.	1406.	1.31	5363.	49.0	19.16
20.	263.	1456.	1.34	5514.	49.4	19.07
21.	263.	1511.	1.38	5673.	49.8	19.02
22.	262.	1567.	1.42	5831.	50.3	18.88
23.	262.	1629.	1.47	6027.	50.9	18.87
24.	260.	1688.	1.50	6231.	51.1	18.77
25.	260.	1750.	1.55	6435.	51.8	18.78
26.	258.	1809.	1.59	6661.	52.3	18.47
27.	257.	1869.	1.63	6910.	52.4	18.37
28.	254.	1928.	1.68	7129.	53.1	18.21
29.	253.	1983.	1.72	7378.	53.2	18.25
30.	249.	2040.	1.77	7612.	53.6	18.12

Table XV

COMBUSTION PRODUCTS FORMED FROM FSP-1-IC-2
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-1-IC-2
 SAMPLE MASS AVG 17.5677
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME(MIN)	DS	CO(PPMV)	CO ₂ (%)	HC(PPMV)	NOX(PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	1.	0.	0.00	11.	0.1	20.69
2.	20.	0.	0.00	131.	0.4	20.74
3.	89.	0.	0.02	544.	2.3	20.70
4.	177.	0.	0.03	932.	2.5	20.77
5.	230.	2.	0.04	1143.	2.6	20.65
6.	256.	7.	0.05	1393.	2.9	20.55
7.	266.	13.	0.06	1658.	3.3	20.66
8.	268.	21.	0.07	1951.	3.7	20.76
9.	269.	28.	0.09	2283.	4.3	20.72
10.	268.	35.	0.10	2519.	5.0	20.67
11.	268.	43.	0.11	2702.	5.9	20.62
12.	267.	50.	0.13	2865.	6.5	20.58
13.	269.	57.	0.14	2974.	7.1	20.55
14.	274.	66.	0.15	3120.	7.7	20.44
15.	273.	75.	0.15	3153.	8.2	20.39
16.	274.	86.	0.16	3202.	8.7	20.42
17.	272.	96.	0.16	3179.	9.2	20.42
18.	271.	106.	0.17	3233.	9.8	20.47
19.	269.	116.	0.17	3227.	10.3	20.50
20.	265.	126.	0.18	3224.	10.9	20.50
21.	264.	135.	0.18	3208.	11.4	20.47
22.	263.	144.	0.19	3220.	11.9	20.46
23.	261.	153.	0.19	3178.	12.4	20.43
24.	257.	161.	0.20	3114.	12.9	20.53
25.	256.	170.	0.20	3105.	13.4	20.54
26.	253.	179.	0.20	3003.	13.9	20.53
27.	250.	187.	0.21	2980.	14.5	20.46
28.	249.	195.	0.21	2929.	14.9	20.53
29.	247.	203.	0.22	2913.	15.4	20.53
30.	245.	210.	0.22	2898.	15.9	20.58

Table XVI

COMBUSTION PRODUCTS FORMED FROM FSP-2-IC-1
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-2-IC-1
 SAMPLE MASS AVG 13.2391
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM². VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME(MIN)	DS	CO(PPMV)	CO ₂ (%)	HC(PPMV)	NOX(PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	53.	36.	0.05	244.	3.7	20.99
2.	130.	126.	0.19	1377.	8.6	20.81
3.	187.	249.	0.36	2539.	14.8	20.67
4.	221.	328.	0.49	3206.	17.1	20.52
5.	239.	379.	0.58	3518.	18.4	20.40
6.	247.	438.	0.68	3755.	19.2	20.26
7.	242.	522.	0.77	3921.	20.1	20.08
8.	230.	601.	0.84	4069.	20.8	20.00
9.	217.	678.	0.93	4149.	21.4	19.85
10.	204.	754.	1.00	4198.	22.2	19.70
11.	192.	825.	1.07	4266.	23.3	19.59
12.	184.	893.	1.14	4333.	24.1	19.41
13.	176.	955.	1.20	4386.	24.7	19.41
14.	168.	1019.	1.28	4416.	25.2	19.25
15.	161.	1081.	1.35	4439.	25.8	19.11
16.	154.	1141.	1.43	4416.	26.5	19.00
17.	149.	1190.	1.49	4447.	26.9	19.03
18.	145.	1228.	1.55	4462.	27.2	18.82
19.	141.	1264.	1.61	4484.	27.7	18.67
20.	137.	1297.	1.67	4537.	27.9	18.63
21.	135.	1331.	1.73	4605.	28.3	18.60
22.	132.	1363.	1.78	4658.	28.7	18.47
23.	128.	1395.	1.84	4718.	29.1	18.41
24.	125.	1425.	1.90	4779.	29.2	18.34
25.	122.	1455.	1.97	4764.	29.7	18.16
26.	119.	1483.	2.03	4804.	30.0	18.08
27.	116.	1513.	2.10	4845.	30.3	17.97
28.	113.	1544.	2.17	4886.	30.7	17.87
29.	111.	1575.	2.24	4928.	31.0	17.76
30.	108.	1608.	2.32	4970.	31.4	17.65

Table XVII

COMBUSTION PRODUCTS FORMED FROM FSP-2-IC-1
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-2-IC-1
 SAMPLE MASS AVG 15.4281
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	1.	0.	0.01	0.	0.0	20.84
2.	44.	0.	0.01	210.	0.1	20.82
3.	84.	0.	0.02	662.	0.4	20.84
4.	109.	0.	0.04	1077.	0.6	20.73
5.	131.	2.	0.05	1528.	1.1	20.63
6.	147.	7.	0.06	2059.	1.5	20.67
7.	160.	13.	0.08	2633.	1.9	20.70
8.	168.	20.	0.09	2888.	2.3	20.71
9.	174.	28.	0.10	3053.	2.6	20.63
10.	179.	36.	0.11	3155.	2.9	20.51
11.	181.	45.	0.12	3204.	3.2	20.35
12.	182.	55.	0.12	3237.	3.5	20.37
13.	179.	64.	0.12	3279.	3.9	20.52
14.	176.	76.	0.13	3290.	4.2	20.58
15.	174.	87.	0.13	3315.	4.5	20.52
16.	170.	98.	0.14	3335.	4.9	20.54
17.	165.	109.	0.14	3342.	5.2	20.51
18.	161.	120.	0.15	3339.	5.6	20.47
19.	157.	131.	0.15	3344.	5.9	20.52
20.	153.	141.	0.16	3320.	6.2	20.52
21.	148.	152.	0.16	3305.	6.5	20.55
22.	145.	162.	0.16	3285.	6.8	20.51
23.	141.	172.	0.17	3282.	7.1	20.52
24.	138.	182.	0.17	3249.	7.4	20.50
25.	136.	192.	0.18	3226.	7.7	20.40
26.	133.	202.	0.18	3172.	8.0	20.43
27.	130.	212.	0.19	3072.	8.3	20.29
28.	128.	214.	0.19	3038.	8.6	20.33
29.	125.	225.	0.20	2997.	8.8	20.25
30.	123.	236.	0.20	2982.	9.1	20.29

Table XVIII

COMBUSTION PRODUCTS FORMED FROM FSP-2-IC-2
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-2-IC-2
 SAMPLE MASS AVG 16.9573
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	11.	6.	0.02	189.	1.3	21.00
2.	77.	43.	0.06	543.	4.4	20.95
3.	169.	97.	0.14	1006.	8.7	20.92
4.	335.	139.	0.24	1663.	13.8	20.86
5.	381.	185.	0.34	2393.	17.1	20.77
6.	394.	240.	0.42	2800.	19.8	20.59
7.	398.	302.	0.50	3238.	22.7	20.58
8.	407.	384.	0.59	3472.	25.5	20.40
9.	416.	482.	0.69	3653.	29.6	20.09
10.	410.	586.	0.78	3736.	33.2	20.08
11.	398.	657.	0.86	3781.	36.2	19.86
12.	383.	720.	0.93	3857.	38.7	19.81
13.	373.	780.	0.99	3947.	40.8	19.70
14.	365.	856.	1.03	4091.	42.0	19.51
15.	356.	934.	1.08	4189.	43.6	19.41
16.	347.	1016.	1.12	4287.	44.6	19.44
17.	338.	1096.	1.17	4347.	45.8	19.21
18.	330.	1172.	1.21	4430.	47.1	19.18
19.	323.	1243.	1.26	4498.	48.5	19.17
20.	317.	1315.	1.31	4544.	49.8	19.05
21.	313.	1381.	1.35	4611.	50.7	19.05
22.	309.	1444.	1.40	4657.	51.9	19.02
23.	303.	1510.	1.45	4710.	53.4	18.88
24.	299.	1576.	1.50	4747.	53.9	18.83
25.	294.	1640.	1.55	4808.	55.2	18.86
26.	289.	1704.	1.60	4891.	56.3	18.73
27.	286.	1768.	1.64	4928.	57.3	18.65
28.	282.	1832.	1.68	4921.	57.9	18.57
29.	277.	1893.	1.73	4966.	59.0	18.34
30.	273.	1958.	1.78	4951.	59.7	18.29

Table XIX

COMBUSTION PRODUCTS FORMED FROM FSP-2-IC-2
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL PVC-FSP-2-IC-2
 SAMPLE MASS AVG 16.0654
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6 x .16

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	4.	0.	0.00	12.	0.1	20.78
2.	30.	0.	0.01	131.	0.7	20.82
3.	54.	0.	0.02	329.	2.8	20.94
4.	94.	0.	0.02	567.	3.5	20.88
5.	153.	0.	0.04	863.	3.6	20.75
6.	223.	2.	0.05	1108.	3.5	20.81
7.	247.	9.	0.06	1399.	3.7	20.89
8.	260.	17.	0.07	1678.	4.1	20.83
9.	267.	25.	0.08	1887.	4.5	20.85
10.	269.	32.	0.09	2103.	5.0	20.86
11.	267.	38.	0.10	2390.	5.7	20.83
12.	267.	46.	0.11	2569.	6.2	20.92
13.	266.	53.	0.12	2759.	6.8	20.82
14.	263.	62.	0.14	2927.	7.4	20.88
15.	261.	71.	0.15	3049.	8.0	20.70
16.	257.	79.	0.15	3144.	8.5	20.68
17.	252.	88.	0.16	3206.	9.0	20.70
18.	249.	98.	0.16	3271.	9.5	20.72
19.	247.	107.	0.17	3328.	10.1	20.64
20.	244.	115.	0.18	3350.	10.6	20.63
21.	241.	125.	0.18	3378.	11.2	20.63
22.	238.	133.	0.19	3363.	11.7	20.62
23.	235.	142.	0.19	3354.	12.2	20.59
24.	233.	150.	0.20	3315.	12.7	20.57
25.	230.	159.	0.20	3251.	13.3	20.55
26.	228.	167.	0.20	3205.	13.7	20.53
27.	225.	176.	0.21	3179.	14.2	20.52
28.	224.	184.	0.21	3135.	14.7	20.52
29.	221.	191.	0.21	3147.	15.3	20.52
30.	219.	199.	0.22	3097.	15.8	20.52

Table XX

COMBUSTION PRODUCTS FORMED FROM AL-IC-1
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL AL-IC-1
 SAMPLE MASS AVG 9.1019
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 X 7.6

AVERAGE

TIME(MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	2.	5.	0.03	10.	1.2	20.99
2.	12.	34.	0.08	35.	4.1	20.95
3.	20.	55.	0.12	48.	7.1	20.82
4.	27.	73.	0.18	55.	9.4	20.73
5.	33.	91.	0.23	66.	11.3	20.70
6.	39.	111.	0.29	124.	12.7	20.59
7.	45.	126.	0.33	197.	13.8	20.49
8.	50.	145.	0.38	284.	14.7	20.55
9.	55.	162.	0.41	413.	15.1	20.44
10.	59.	183.	0.44	536.	15.6	20.37
11.	63.	208.	0.47	667.	15.9	20.38
12.	67.	233.	0.50	804.	16.3	20.23
13.	71.	262.	0.54	923.	16.7	20.33
14.	74.	292.	0.57	1049.	17.0	20.22
15.	77.	321.	0.60	1181.	17.4	20.08
16.	79.	358.	0.63	1308.	17.5	20.17
17.	81.	393.	0.66	1433.	17.8	20.08
18.	84.	433.	0.69	1565.	18.1	20.06
19.	85.	489.	0.72	1663.	18.3	19.95
20.	87.	554.	0.75	1766.	18.6	19.87
21.	89.	638.	0.78	1849.	18.8	19.88
22.	91.	730.	0.81	1931.	19.2	19.88
23.	92.	819.	0.84	2007.	19.3	19.78
24.	94.	908.	0.87	2079.	19.7	19.70
25.	95.	1004.	0.90	2234.	19.9	19.56
26.	96.	1105.	0.94	2302.	20.1	19.54
27.	97.	1200.	0.96	2368.	20.4	19.51
28.	98.	1278.	0.99	2446.	20.7	19.37
29.	99.	1356.	1.02	2477.	20.9	19.51
30.	100.	1405.	1.05	2634.	21.2	19.44

Table XXI
COMBUSTION PRODUCTS FORMED FROM Al-IC-1
UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL AL-IC-1
SAMPLE MASS AVG 9.1910
IMPOSED EXPOSURE CONDITION NONFLAMING
FLUX 2.5 W/CM², VERTICAL
DIMENSIONS 7.6 x 7.6

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	0.	0.	0.00	0.	0.0	21.00
2.	6.	0.	0.00	0.	0.0	20.87
3.	18.	0.	0.01	9.	0.1	20.92
4.	26.	0.	0.01	18.	0.4	20.94
5.	30.	0.	0.01	22.	0.7	20.82
6.	34.	0.	0.01	26.	1.1	20.80
7.	38.	0.	0.01	30.	1.5	20.85
8.	42.	0.	0.01	34.	1.7	20.85
9.	45.	0.	0.01	36.	2.0	20.86
10.	48.	1.	0.02	39.	2.2	20.92
11.	51.	2.	0.02	40.	2.4	20.94
12.	54.	3.	0.02	42.	2.6	20.93
13.	56.	4.	0.02	43.	2.8	20.92
14.	58.	5.	0.02	41.	3.0	20.98
15.	60.	6.	0.02	46.	3.1	20.93
16.	62.	7.	0.02	49.	3.3	20.80
17.	64.	9.	0.02	51.	3.5	20.86
18.	66.	10.	0.02	53.	3.7	20.94
19.	67.	11.	0.02	54.	3.9	20.87
20.	68.	12.	0.02	55.	4.0	20.98
21.	70.	14.	0.03	56.	4.3	21.00
22.	71.	15.	0.03	56.	4.5	21.00
23.	72.	16.	0.03	57.	4.6	21.00
24.	73.	18.	0.03	59.	4.8	20.93
25.	74.	19.	0.03	60.	5.0	20.86
26.	74.	20.	0.03	60.	5.2	20.81
27.	74.	22.	0.03	61.	5.4	20.80
28.	75.	22.	0.03	62.	5.6	20.80
29.	75.	24.	0.03	62.	5.8	20.82
30.	76.	25.	0.03	62.	6.0	20.84

Table XXII

COMBUSTION PRODUCTS FORMED FROM A1-IC-2
UNDER FLAME EXPOSURE CONDITIONS

MATERIAL AL-IC-2
 SAMPLE MASS AVG 8.4956
 IMPOSED EXPOSURE CONDITION FLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 x 7.6

AVERAGE

TIME(MIN)	DS	CO(PPMV)	CO ₂ (%)	HC(PPMV)	NOX(PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	21.	6.	0.03	31.	1.8	20.80
2.	91.	46.	0.08	154.	7.6	20.77
3.	132.	69.	0.12	261.	10.7	20.62
4.	162.	86.	0.18	355.	13.1	20.47
5.	177.	103.	0.22	429.	15.0	20.51
6.	185.	121.	0.27	496.	17.1	20.55
7.	188.	138.	0.31	551.	18.8	20.40
8.	187.	155.	0.36	595.	20.5	20.31
9.	185.	172.	0.40	631.	22.3	20.38
10.	181.	187.	0.45	661.	24.1	20.23
11.	177.	203.	0.49	681.	25.4	20.31
12.	172.	212.	0.53	705.	27.6	20.27
13.	167.	229.	0.58	723.	28.9	20.09
14.	163.	247.	0.62	740.	30.4	20.04
15.	158.	263.	0.66	761.	31.7	20.00
16.	154.	280.	0.70	768.	33.2	19.90
17.	150.	297.	0.74	779.	34.3	19.81
18.	146.	315.	0.78	786.	35.5	19.65
19.	143.	333.	0.82	795.	36.9	19.54
20.	140.	351.	0.86	805.	38.0	19.62
21.	138.	370.	0.90	814.	38.8	19.71
22.	135.	389.	0.95	819.	40.1	19.65
23.	133.	407.	0.98	825.	41.1	19.71
24.	130.	425.	1.02	827.	41.9	19.67
25.	129.	441.	1.06	828.	42.8	19.56
26.	126.	458.	1.09	827.	43.6	19.40
27.	125.	473.	1.13	826.	44.2	19.35
28.	123.	488.	1.16	822.	45.1	19.25
29.	121.	503.	1.20	820.	45.7	19.18
30.	119.	518.	1.24	817.	46.4	19.11

Table XXIII

COMBUSTION PRODUCTS FORMED FROM A1-IC-2
 UNDER NONFLAME EXPOSURE CONDITIONS

MATERIAL AL-IC-2
 SAMPLE MASS AVG 8.4462
 IMPOSED EXPOSURE CONDITION NONFLAMING
 FLUX 2.5 W/CM², VERTICAL
 DIMENSIONS 7.6 X 7.6

AVERAGE

TIME (MIN)	DS	CO (PPMV)	CO ₂ (%)	HC (PPMV)	NOX (PPMV)	O ₂ (%)
0.	0.	0.	0.00	0.	0.0	21.00
1.	0.	0.	0.00	0.	0.0	20.78
2.	10.	0.	0.00	16.	0.4	20.69
3.	30.	0.	0.01	113.	2.6	20.75
4.	41.	1.	0.01	176.	3.8	20.73
5.	51.	3.	0.01	218.	4.4	20.60
6.	60.	3.	0.01	251.	4.9	20.62
7.	68.	4.	0.01	272.	5.3	20.69
8.	75.	5.	0.02	288.	5.6	20.65
9.	80.	5.	0.02	302.	5.9	20.67
10.	84.	6.	0.02	313.	6.1	20.56
11.	88.	7.	0.02	325.	6.3	20.33
12.	90.	8.	0.02	330.	6.5	20.45
13.	93.	9.	0.03	339.	6.7	20.40
14.	94.	10.	0.03	346.	6.9	20.43
15.	96.	10.	0.03	351.	7.1	20.40
16.	96.	10.	0.03	355.	7.3	20.45
17.	97.	11.	0.03	359.	7.4	20.47
18.	97.	11.	0.03	360.	7.6	20.33
19.	97.	12.	0.03	361.	7.8	20.37
20.	97.	13.	0.03	363.	7.9	20.32
21.	97.	14.	0.03	363.	8.1	20.32
22.	96.	15.	0.03	362.	8.3	20.17
23.	96.	15.	0.03	361.	8.5	20.02
24.	95.	15.	0.03	364.	8.6	20.16
25.	94.	16.	0.03	359.	8.8	20.20
26.	93.	17.	0.03	360.	8.9	20.16
27.	93.	18.	0.03	357.	9.1	20.03
28.	92.	18.	0.03	355.	9.2	20.24
29.	92.	19.	0.03	351.	9.4	20.29
30.	90.	20.	0.04	348.	9.5	20.29

DISTRIBUTION LIST

	<u>No. of Copies</u>
Naval Ship Engineering Center, Code N65197 National Center, Building No. 2 Room 5E52 Washington, D. C. 20362	2
Naval Sea Systems Command, Code N00024 Department of the Navy Washington, DC 20360 Attn: NAVSEA 03511	1
Naval Surface Weapons Center, Code N60921 Silver Spring, Maryland 20910 Attn: Dr. Angel	1
Naval Research Laboratory, Code N00173 Washington, DC 20390 Attn: Chemistry Div. Code 6100	1
Naval Research Laboratory, Code N00173 Washington, DC 20390 Attn: Non-metallics Div.	1
Naval Ship Research and Development Center, Code N00162 Bethesda, Maryland Attn: Non-metallics Code 284	1
Office of Naval Research, Code N00014 Ballston Tower #1, Code 472 Arlington, Virginia 22217	1
Naval Sea Systems Command, Code N00024 Department of the Navy Washington, DC 20360 Attn: NAVSEA 024	1
Defense Documentation Center, Code SL4200 Cameron Station Alexandria, Virginia 22314	12

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Flame- and Smoke-Retardant Polymer Systems,		5. TYPE OF REPORT & PERIOD COVERED Second Quarterly Report, no. 2, August - October 1976,
7. AUTHOR(s) Leo Parts and Catherine A. Thompson		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Monsanto Research Corporation Dayton Laboratory, 1515 Nicholas Road Dayton, Ohio 45407		8. CONTRACT OR GRANT NUMBER(s) N00024-76-C-5336
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy, Code N00024 Naval Sea Systems Command SEA 0253D Washington, D. C. 20362		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) DCASD, Dayton Building 5, Code S3605A Dayton, Ohio		12. REPORT DATE 26 April 1977
		13. NUMBER OF PAGES 53
		15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release. Distribution Unlimited.		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)		
Flame retardant	Neoprene	Carbon dioxide
Smoke retardant	Ignition temperatures	Nitrogen oxides
Fire safety	Smoke	Hydrogen chloride
Polymers	Combustion products	Intumescent coatings
Polyvinyl chloride	Carbon monoxide	Fire-retardant coatings
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)		
Experimental smoke-retardant PVC compositions and a reference base polymer were coated with alkyd- and epoxy-based intumescent paints. Specimens were tested in an NBS smoke density chamber under flame and nonflame exposure conditions. The smoke optical density, and the concentrations of CO, CO₂, NO_x, hydrocarbons, hydrogen chloride and oxygen were monitored during these tests. Although the coatings reduced smoke formation from the base polymer, they had an adverse effect on the performance of the smoke-retardant compositions. The commercial coatings used in this work were found to generate significant quan-		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

401 865

LB

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Item 20 Abstract (cont'd)

tities of smoke. Other, recently developed coatings will be used in projected work.

The intumescent coatings reduced the rates of carbon monoxide and hydrogen chloride formation, especially under nonflame exposure to a radiant energy source.

The coatings contributed small amounts of nitrogen oxides (NO_x) to the combustion products.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)