

AD-A039 537

HARRY DIAMOND LABS ADULPHI MD  
CHARGE YIELD AND DOSE EFFECTS IN MOS CAPACITORS AT 80 K.(U)  
MAY 77 H E BOESCH, J M MCGARRITY  
HDL-TR-1806

F/G 20/12

UNCLASSIFIED

NL

1 of 1  
AD  
A039537



END

DATE  
FILMED  
6-77

ADA 039537

THE UNIVERSITY OF CHICAGO  
LIBRARY  
540 EAST 57TH STREET  
CHICAGO, ILL. 60637  
U.S.A.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| REPORT DOCUMENTATION PAGE                                                                                                                                                                                                                                                                                                                                                                                                                                                                    |                       | READ INSTRUCTIONS<br>BEFORE COMPLETING FORM                                           |  |
|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------|---------------------------------------------------------------------------------------|--|
| 1. REPORT NUMBER<br>HDL-TR-1806                                                                                                                                                                                                                                                                                                                                                                                                                                                              | 2. GOVT ACCESSION NO. | 3. RECIPIENT'S CATALOG NUMBER                                                         |  |
| 4. TITLE (and Subtitle)<br>Charge Yield and Dose Effects in MOS Capacitors at 80 K                                                                                                                                                                                                                                                                                                                                                                                                           |                       | 5. TYPE OF REPORT & PERIOD COVERED<br>Technical Report                                |  |
| 7. AUTHOR(s)<br>Harold E. Boesch, Jr.<br>James M. McGarrity                                                                                                                                                                                                                                                                                                                                                                                                                                  |                       | 6. PERFORMING ORG. REPORT NUMBER                                                      |  |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS<br>Harry Diamond Laboratories<br>2800 Powder Mill Road<br>Adelphi, MD 20783                                                                                                                                                                                                                                                                                                                                                                      |                       | 8. CONTRACT OR GRANT NUMBER(s)                                                        |  |
| 11. CONTROLLING OFFICE NAME AND ADDRESS<br>Director<br>Defense Nuclear Agency<br>Washington, DC 20301                                                                                                                                                                                                                                                                                                                                                                                        |                       | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS<br>Program Ele: 6.27.04.H |  |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)                                                                                                                                                                                                                                                                                                                                                                                                                  |                       | 12. REPORT DATE<br>May 77                                                             |  |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |                       | 13. NUMBER OF PAGES<br>33                                                             |  |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |                       | 15. SECURITY CLASS. (of this report)<br>Unclassified                                  |  |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |                       | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE                                            |  |
| 16. DISTRIBUTION STATEMENT (of this Report)<br><br>Approved for public release; distribution unlimited.                                                                                                                                                                                                                                                                                                                                                                                      |                       |                                                                                       |  |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)                                                                                                                                                                                                                                                                                                                                                                                                   |                       |                                                                                       |  |
| 18. SUPPLEMENTARY NOTES<br>HDL Project: 236T28 DRCMS Code: 6970002211556<br>This work was sponsored by the U.S. Army Materiel Development and Readiness Command and the Defense Nuclear Agency under Z99QAXT007, Work Unit 64, Unit Title "TRANSEFF."                                                                                                                                                                                                                                        |                       |                                                                                       |  |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number)<br>MOS capacitors      Hole transport<br>Low temperature<br>Radiation damage<br>Charge yield                                                                                                                                                                                                                                                                                                              |                       |                                                                                       |  |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number)<br>The response of metal-oxide semiconductor capacitors to short-pulse high-energy electron irradiation was measured at 80 K. It was confirmed that radiation-generated holes are almost totally retained in the SiO <sub>2</sub> layer regardless of oxide processing; this retention was exploited to determine carrier yield as a function of applied electric field. Evidence was found that the holes |                       |                                                                                       |  |

DD FORM 1 JAN 75 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

1 SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

over  
bpg

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

5100

1,000,000

undergo an initial displacement under an applied field immediately following carrier generation (9.5 nm at  $10^5$  V/cm). Samples were subjected to pulsed irradiation at 80 K to accumulated doses above  $10^5$  rads( $\text{SiO}_2$ ) and mechanisms which limit hole buildup above  $5 \times 10^4$  rads( $\text{SiO}_2$ ) were explored. Electron-hole recombination in a low field region of the  $\text{SiO}_2$  was identified as an important process and was modeled. Other mechanisms discussed include electron injection, field- and temperature-activated hole transport, applied field collapse, and dielectric breakdown.

50,000

A

|                            |                                                   |
|----------------------------|---------------------------------------------------|
| ACCESSION                  |                                                   |
| NTIS                       | White Section <input checked="" type="checkbox"/> |
| DOC                        | Buff Section <input type="checkbox"/>             |
| UNANNOUNCED                | <input type="checkbox"/>                          |
| JUSTIFICATION              |                                                   |
| CAUTION/AVAILABILITY CODES |                                                   |
| SL                         | AVAIL. INFO/SPECIAL                               |
| A                          |                                                   |

## CONTENTS

|                                                        | <u>Page</u> |
|--------------------------------------------------------|-------------|
| 1. INTRODUCTION . . . . .                              | 5           |
| 2. SAMPLES AND EXPERIMENTAL TECHNIQUES . . . . .       | 6           |
| 3. CHARGE-YIELD MEASUREMENT . . . . .                  | 7           |
| 3.1 Field Dependence of Hole Yield . . . . .           | 7           |
| 3.2 Initial Hole Displacement . . . . .                | 10          |
| 4. DOSE DEPENDENCE OF CHARGE BUILDUP . . . . .         | 13          |
| 4.1 Measurements and Results . . . . .                 | 13          |
| 4.2 Discussion . . . . .                               | 15          |
| 4.2.1 Linear Region . . . . .                          | 15          |
| 4.2.2 Saturation Region . . . . .                      | 16          |
| 4.2.2.1 Recombination in Low-Field Region . . . . .    | 16          |
| 4.2.2.2 Electron Injection at High Fields . . . . .    | 21          |
| 4.2.2.3 Hole Transport . . . . .                       | 22          |
| 4.2.2.4 Collapse of Applied Field . . . . .            | 23          |
| 4.2.2.5 Dielectric Breakdown . . . . .                 | 24          |
| 4.2.2.6 Applicability to Higher Temperatures . . . . . | 24          |
| 5. CONCLUSIONS . . . . .                               | 25          |
| ACKNOWLEDGEMENTS . . . . .                             | 25          |
| LITERATURE CITED . . . . .                             | 25          |
| DISTRIBUTION . . . . .                                 | 27          |

## FIGURES

|   |                                                                                                                                                 |    |
|---|-------------------------------------------------------------------------------------------------------------------------------------------------|----|
| 1 | Flatband-voltage shift and corresponding hole yield in MOS capacitors irradiated at 80 K . . . . .                                              | 9  |
| 2 | Normalized flatband-voltage shift and equivalent flatband shift for $E = 1$ MV/cm and $L = 100$ nm for various MOS capacitors at 80 K . . . . . | 14 |
| 3 | Flatband-voltage shift, $\Delta V_{FB}$ , 1 ms after irradiation of HAC p-type and n-type MOS capacitors at 80 K . . . . .                      | 14 |

# CONTENTS (Cont'd)

|                                                                                                                                 | <u>Page</u> |
|---------------------------------------------------------------------------------------------------------------------------------|-------------|
| 4 Flatband-voltage shift, $\Delta V_{FB}$ , as function of time after first LINAC pulse delivered to HAC dry-n MOS capacitors . | 15          |
| 5 Model for limitation of charge buildup in an oxide layer                                                                      | 17          |
| 6 Calculated field and hole density profiles in the oxide as a function of dose at 80 K . . . . .                               | 20          |
| 7 Comparison of model calculations and experimental results on the flatband-voltage shift . . . . .                             | 20          |

## TABLES

|                                                              |    |
|--------------------------------------------------------------|----|
| I MOS Capacitor SiO <sub>2</sub> Characteristics . . . . .   | 6  |
| II Initial Hole Displacement in MOS Samples at ~80 K . . . . | 11 |

## 1. INTRODUCTION

Metal-oxide semiconductor (MOS) devices, such as charge-coupled devices (CCD's) and MOSFET's (MOS field-effect transistors), are being investigated for use in imaging, signal processing, and detector preamplifier applications in which the detector and its immediately associated electronics are operated at low temperatures ( $\leq 80$  K). Recent experiments on MOS capacitors and devices at  $\sim 80$  K have established that, when hole-electron pairs are generated in the  $\text{SiO}_2$  insulating layer by ionizing radiation, the electrons are rapidly swept out of the oxide while the holes remain essentially immobile ("frozen in") at or near their point of creation.<sup>1,2,3</sup> As a result, most of the holes generated by the radiation remain in place in the oxide layer for significant times and cause relatively large flatband- or threshold-voltage shifts per unit dose in MOS structures. (A flatband voltage shift of  $\sim -1$  V is expected for a  $10\text{-krad}(\text{SiO}_2)$  dose in a  $100\text{-nm}$  oxide.) These shifts threaten device operation at doses well below 100 krad. In contrast to the highly process-dependent "permanent" trapping of a small fraction (typically 1 to 10 percent) of the radiation-generated holes observed at room temperature in "hard" MOS oxides, the retention of the holes in  $\text{SiO}_2$  at  $\sim 80$  K is largely process independent<sup>2</sup> and results from a strongly temperature-dependent hole-transport mechanism.<sup>1,3,4</sup> Since the yield of electron-hole pairs generated in an MOS oxide per unit radiation dose is believed<sup>5</sup> to be an intrinsic property of amorphous  $\text{SiO}_2$ , this yield also should be process independent. Therefore, if MOSFET's, MOS integrated circuits (IC's), or charge-coupled devices with pure  $\text{SiO}_2$  gate-insulator layers are operated and irradiated at low temperatures, they will suffer relatively large oxide-charge buildups whether or not they have been hardened to charge trapping at room temperature.

---

<sup>1</sup>H. E. Boesch, Jr., F. B. McLean, J. M. McGarrity, and G. A. Ausman, Jr., *IEEE Trans. Nucl. Sci.* **NS-22**, 2163 (1975).

<sup>2</sup>H. H. Sander and B. L. Gregory, *IEEE Trans. Nucl. Sci.* **NS-22**, 2157 (1975).

<sup>3</sup>R. C. Hughes, E. P. Eer Nisse, and H. J. Stein, *IEEE Trans. Nucl. Sci.* **NS-22**, 2227 (1975).

<sup>4</sup>F. B. McLean, H. E. Boesch, Jr., and J. M. McGarrity, *Hole Transport and Recovery Characteristics of MOS Gate Insulators*, *IEEE Nuclear and Space Radiation Effects Conference* (July 1976).

<sup>5</sup>G. A. Ausman, Jr., and F. B. McLean, *Appl. Phys. Lett.* **26**, 173 (1975).

The present report discusses two related investigations of radiation-induced charge buildup in  $\text{SiO}_2$  at  $\sim 80$  K. In the first study, the retention of holes at low temperature was exploited to provide a direct measure of hole-electron pair yield per unit radiation dose at low temperature as a function of electric field for high-energy ionizing radiation. In the second study, the response of MOS capacitors to short-pulse high-dose irradiation at  $\sim 80$  K was investigated, and mechanisms which impose limits on the oxide-charge buildup were examined.

## 2. SAMPLES AND EXPERIMENTAL TECHNIQUES

Dry-grown oxide samples were provided by Hughes Aircraft Corporation (HAC), Northrop Research and Technology Center (NRTC), and a proprietary source supported by the Defense Nuclear Agency (DNA). HAC also supplied a wet-oxide sample representative of the process under development in their hardened complementary-MOS/silicon-on-sapphire program. The dry oxides were thermally grown at  $1000^\circ\text{C}$  and the wet oxide was pyrogenically grown at  $950^\circ\text{C}$ , usually on n-type Si (see table I). Aluminum gate electrodes were deposited, and the resulting MOS capacitors were bonded to headers without caps.

TABLE I. MOS CAPACITOR  $\text{SiO}_2$  CHARACTERISTICS

| Identifier | Gate deposition | Post anneal                              | Oxide thickness (nm) |
|------------|-----------------|------------------------------------------|----------------------|
| DNA No. 1  | filament        | A, 15 m, $800^\circ\text{C}$             | 72.5                 |
| DNA No. 2  | filament        | None                                     | 65.5                 |
| HAC dry n  | C crucible      | None                                     | 87.5                 |
| HAC dry p  | C crucible      | None                                     | 87.5                 |
| HAC wet n  | C crucible      | $\text{N}_2$ , 20 m, $925^\circ\text{C}$ | 96.5                 |
| NRTC 850   | e-beam          | None                                     | 85                   |
| NRTC 671   | e-beam          | None                                     | 67                   |
| NRTC 1538  | e-beam          | None                                     | 154                  |

The experiments were performed with the electron linear accelerator (LINAC) at the Armed Forces Radiobiology Research Institute (AFRRI). The LINAC produced a nominal 12- to 13-MeV 1-A electron beam with a pulse width of 4 ns. Multiple pulses could be delivered to the sample at a rate of 60/s. Sample dose per pulse was controlled by varying the LINAC-to-sample distance. A thin-foil Cu calorimeter was used for pulse-to-pulse electron-beam dosimetry. Teflon:CaF<sub>2</sub> thin-disc thermoluminescent dosimeters were employed for absolute dose measurements. For the charge-yield experiment, the samples were mounted in a liquid-nitrogen-cooled sample holder under vacuum.<sup>6</sup> For the high-dose experiments, the samples were submerged directly in a liquid-nitrogen bath to insure maximum thermal transfer. For both experiments, data were taken only on the first pulse delivered to a sample. A fast high-frequency capacitance-voltage (C-V) measuring apparatus<sup>6,7</sup> recorded the preirradiation C-V characteristics and monitored these characteristics as a function of time either after a single radiation pulse, or, sometimes, at 1 and 12 ms after each individual radiation pulse in a multiple-pulse burst. The MOS capacitance of the sample was monitored by a phase-sensitive detector system operating at 5 MHz. The C-V characteristics were recorded on oscilloscopes by monitoring the capacitance as a 0.1 ms voltage ramp was applied to the capacitor. The fast C-V system was intercalibrated with a Boonton 71A capacitance meter and found capable of accurately reproducing the deep-depletion C-V trace. From the C-V data, the radiation-induced flatband-voltage shift,  $\Delta V_{FB}$ , was extracted.

### 3. CHARGE-YIELD MEASUREMENT

#### 3.1 Field Dependence of Hole Yield

The field (bias) dependence of the yield of charge carriers in SiO<sub>2</sub> was measured by Curtis, Srour and Chiu<sup>8</sup> at room temperature by a charge-collection technique and low-energy (~4-keV) electron irradiation. Ausman and McLean<sup>5</sup> demonstrated that these results were consistent with a hole-electron pair-creation energy  $W_0 \sim 18$  eV/pair,

<sup>5</sup>G. A. Ausman, Jr., and F. B. McLean, *Appl. Phys. Lett.* **26**, 173 (1975).

<sup>6</sup>H. E. Boesch, Jr., *Development of Apparatus for Performing Rapid Capacitance-Voltage Measurements on MIS Structures*, Harry Diamond Laboratories TM-76-33 (December 1976).

<sup>7</sup>F. B. McLean, H. E. Boesch, Jr., P. S. Winokur, J. M. McGarrity, and R. B. Oswald, Jr., *IEEE Trans. Nucl. Sci.* **NS-21**, 47 (1974).

<sup>8</sup>O. L. Curtis, Jr., J. R. Srour, and K. Y. Chiu, *J. Appl. Phys.* **45**, 4506 (1974).

which in turn agrees with results of a model for the ionization process based on plasmon creation. Following creation, the actual yield of free carriers is determined by field-aided escape (i.e., aided by applied bias) of carriers from bimolecular recombination in the high ionization-density regions along the tracks of the incident kilovolt electrons.<sup>5</sup> Snowden et al<sup>9</sup> measured collected charge in SiO<sub>2</sub> capacitors at room temperature using high-energy ionizing radiation (30-MeV LINAC electrons). Their results are again consistent with W<sub>0</sub> = 18 eV/pair. In contrast to kiloelectron volt electron irradiation, which produces high ionization-density regions along the relatively short tracks of the incident particles, the very high energy LINAC electron beam produces widely dispersed point ionization in the SiO<sub>2</sub> similar to that which would be produced by energetic photon irradiation.

In this experiment, hole yield in the SiO<sub>2</sub> induced by 13-MeV LINAC radiation pulses was measured at low temperature by the fast C-V measurement technique. Bias voltages were applied to produce fields from  $-0.6 \times 10^6$  to  $4.7 \times 10^6$  V/cm. To insure that the radiation-generated oxide charge did not significantly perturb the externally applied oxide field, the dose per radiation pulse was maintained below  $3 \times 10^3$  rads(SiO<sub>2</sub>).

The early (~1 ms after pulse) flatband voltage shift  $\Delta V_{FB}$  is plotted in figure 1 as a function of oxide internal field for the DNA No. 1 n-type samples. (Similar results were obtained for NRTC 1538A MOS capacitors.) To correct for pulse-to-pulse dose variations, the  $\Delta V_{FB}$  values have been normalized by the calorimeter readings to a nominal dose of  $2 \times 10^3$  rads(SiO<sub>2</sub>). The flatband shift saturates beyond  $10^6$  V/cm and is essentially symmetrical about the zero V/cm axis.

For a uniform radiation-produced oxide charge density,  $\rho$ , consisting of the holes only,

$$\Delta V_{FB} = - \frac{\rho L^2}{2\epsilon} \quad (1)$$

<sup>5</sup>G. A. Ausman, Jr., and F. B. McLean, *Appl. Phys. Lett.* 26, 173 (1975).

<sup>9</sup>R. E. Leadon, D. P. Snowden, and J. M. Wilkenfeld, *Radiation Effects in Semiconductor and Insulator Materials*, IRT Corporation, Harry Diamond Laboratories CR-76-152-1 (April 1976).

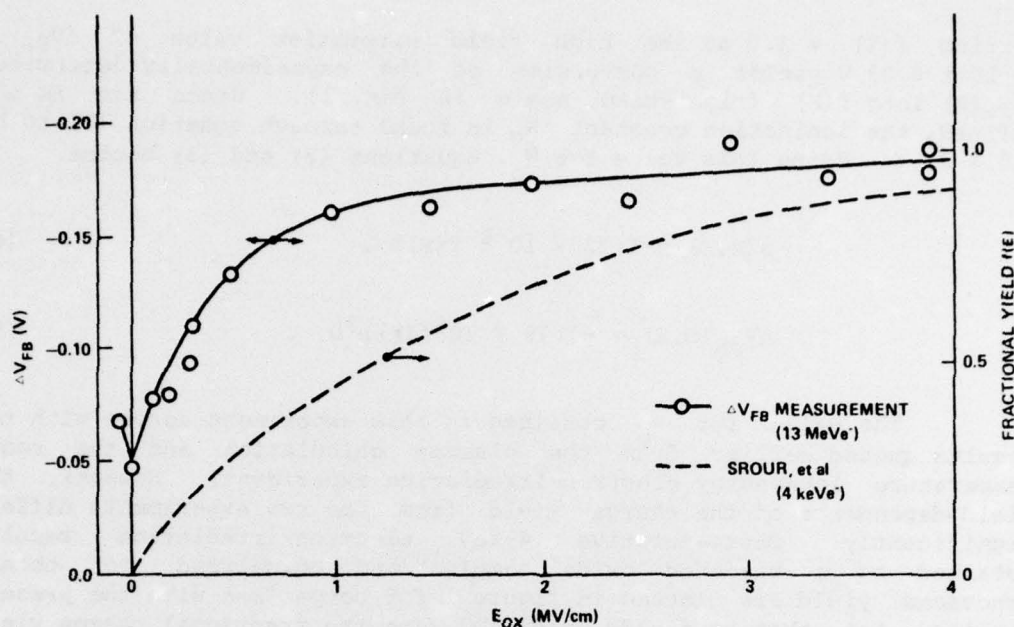


Figure 1. Flatband-voltage shift and corresponding hole yield in MOS capacitors irradiated at 80 K.

where  $L$  is the oxide thickness in centimeters and  $\epsilon$  is the dielectric constant in F/cm. The charge density may in turn be expressed as a function of oxide dose  $D$ , in rads( $\text{SiO}_2$ ), using appropriate material parameters and the electric-field-dependent fraction  $f(E)$  of the radiation-generated holes which escape initial recombination,

$$\rho(D, E) = 2.2 \times 10^{-5} W_O^{-1} f(E) D \quad (2)$$

Then

$$\Delta V_{FB}(D, E) = (-3.23 \times 10^7) f(E) W_O^{-1} L^2 D \quad (3)$$

The fractional hole yield as a function of field,  $f(E)$ , may be obtained from the  $\Delta V_{FB}$  data in figure 1 by assuming that the asymptotic or saturation value of the flatband shift above  $\sim 3 \times 10^6$  V/cm corresponds to all the holes escaping initial recombination; i.e.,  $f(E) = 1.0$ .

Setting  $f(E) = 1.0$  at the high field saturation value of  $\Delta V_{FB} = -0.18 \pm 0.03$  V yields a conversion of the experimentally determined  $\Delta V_{FB}(E)$  into  $f(E)$  (right-hand scale in fig. 1). Since  $f(E)$  is now defined, the ionization constant  $W_0$  is found through equation (3) to be  $(18 \pm 3)$  eV. Using this value for  $W_0$ , equations (2) and (3) become

$$\rho(D, E) = 1.22 \times 10^{-6} f(E) D, \quad (4)$$

$$\Delta V_{FB}(D, E) = -1.79 \times 10^6 f(E) L^2 D. \quad (5)$$

The value for  $W_0$  obtained in this experiment agrees with the results quoted earlier from the plasmon calculation and the room-temperature low-energy electron-irradiation experiment. However, the field dependence of the charge yield from the two experiments differs significantly. Representative 4-keV electron-irradiation results obtained on a hardened oxide sample<sup>10</sup> and normalized to obtain fractional yield are plotted in figure 1 for comparison with the present results. Note that at fields below  $10^6$  V/cm the fractional charge yield produced by the high-energy radiation is much greater than that produced by the low-energy electrons. The present results are adequately explained by a geminate recombination process in which field-dependent rapid recombination takes place between the members of the widely dispersed electron-hole pairs produced by the high energy radiation.\*

### 3.2 Initial Hole Displacement

To this point, it has been assumed that all the holes remain in the oxide after irradiation. However, evidence has been found in this work that a fraction of the holes escapes the oxide immediately following generation, even at  $\sim 80$  K. As indicated in a previous paper,<sup>1</sup> the flatband shifts obtained in identical MOS samples at identical doses under negative and positive biases are almost, but not quite, the same. Results obtained on a number of samples from a pair of such measurements are recorded in table II. In each case, the negative bias shift is 10 to 20 percent less than the positive shift. Initially,

---

\*G. A. Ausman, Jr., private communication.

<sup>1</sup>H. E. Boesch, Jr., F. B. McLean, J. M. McGarrity, and G. A. Ausman, Jr., IEEE Trans. Nucl. Sci. NS-22, 2163 (1975).

<sup>10</sup>J. R. Srour, O. L. Curtis, Jr., and K. Y. Chiu, IEEE Trans. Nucl. Sci. NS-21, No. 6, 73 (1974).

TABLE II. INITIAL HOLE DISPLACEMENT IN MOS SAMPLES AT ~80 K

| Sample    | $\Delta V_{FB+}$<br>(V) | $\Delta V_{FB-}$<br>(V) | E<br>(MV/cm) | Distance<br>(nm) |
|-----------|-------------------------|-------------------------|--------------|------------------|
| DNA No. 1 | -3.5                    | -2.7                    | 1.38         | $9.4 \pm 1.4$    |
| DNA No. 2 | -3.3                    | -2.5                    | 1.53         | $9.0 \pm 1.3$    |
| HAC dry n | -2.7                    | ---                     | 1.14         | $10.9 \pm 2.1$   |
| HAC dry p | ---                     | -2.1                    |              |                  |
| NRTC 850  | -6.2                    | -5.0                    | 1.18         | $9.1 \pm 0.8$    |
| NRTC 1538 | -2.7                    | -2.3                    | 0.98         | $12.3 \pm 3.3$   |

it was assumed that this variation resulted from a decrease in the oxide field under negative bias because of a potential drop across the depletion region in the n-type silicon under inversion or deep-depletion conditions. However, this potential drop virtually disappears during a radiation pulse since the depletion region collapses very quickly as carriers are generated in the silicon and transported through the depletion region.<sup>9</sup> Also, the  $\Delta V_{FB}$  relative decrease at negative biases was exhibited by a pair of samples--HAC dry n and HAC dry p--with identical oxide layers which were irradiated at positive and negative biases respectively, i.e., under accumulation conditions.

The bias effect is adequately explained by postulating that the holes are first transported through extended states in the valence band immediately after the holes are thermalized and before they are captured at a defect site and hopping transport begins. If at a given field the holes are transported an average distance  $d$  in the valence band in an oxide of thickness  $L$ , then under positive bias and uniform field conditions in the oxide, the hole distribution will be uniformly displaced toward the Si. This displacement leaves the zone between  $x = 0$  (where  $x$  is a distance from the metal electrode) and  $x = d$  depleted of holes. Similarly, under negative bias a zone between  $x = L - d$  and  $x = L$  (the Si interface) will be depleted. The corresponding  $\Delta V_{FB}$  values are

$$\Delta V_{FB+} = -\rho/\epsilon \int_d^L x dx = -\rho/2\epsilon (L^2 - d^2), \quad (6)$$

<sup>9</sup>R. E. Leadon, D. P. Snowden, and J. M. Wilkenfeld, *Radiation Effects in Semiconductor and Insulator Materials*, IRT Corporation, Harry Diamond Laboratories CR-76-152-1 (April 1976).

$$\Delta V_{FB-} = -\rho/\epsilon \int_0^{L-d} x dx = -\rho/2\epsilon (L-d)^2. \quad (7)$$

Then

$$f_d = \left| \frac{\Delta V_{FB+} - \Delta V_{FB-}}{\Delta V_{FB+}} \right| = \frac{2d(L-d)}{L^2 - d^2}. \quad (8)$$

Solving for d,

$$d = \frac{Lf_d}{2 - f_d} \quad (9)$$

Values for the initial hole displacement d obtained for several of the MOS samples are presented in table II together with error limits calculated from the estimated probable error in the  $\Delta V_{FB}$  values. The agreement within the error limits implies strongly that the charge-displacement analysis is essentially correct and that  $d \sim 9.5$  nm is appropriate for all the materials examined. If d is assumed to be a schubweg, i.e.,  $d = \mu_H \tau_H E$  where  $\mu_H$  is the intrinsic hole mobility,  $\tau_H$  is the hole dwell time in the valence band, and E is the electric field, then the product  $\mu_H \tau_H \approx 7 \times 10^{-3}$  V/cm under these conditions. Unfortunately, the measurements were not performed over a sufficient range of electric field to determine whether d is a schubweg or perhaps a field-independent mean free path.

The error,  $\eta$ , introduced by charge displacement in the measurement of total hole yield under positive bias, is easily found from an extension of the analysis above to be

$$\begin{aligned} \eta &= (\rho L^2/\epsilon - \Delta V_{FB+})/(\rho L^2/\epsilon) \\ &= d^2/L^2 \end{aligned} \quad (10)$$

For a 72.7-nm oxide and  $d = 9.5$  nm,  $\eta = 0.017$ . Therefore, initial charge displacement had a negligible effect on the charge-yield results (fig. 1).

#### 4. DOSE DEPENDENCE OF CHARGE BUILDUP

##### 4.1 Measurements and Results

The response of MOS capacitors to pulsed irradiation at 80 K was measured as a function of dose, applied bias, and time after irradiation.

In the first experiment, a variety of MOS samples (table I) were irradiated at various biases to doses in the  $10^3$  to  $10^6$  rad( $\text{SiO}_2$ ) range and  $\Delta V_{\text{FB}}$  was recorded at 1 ms after the radiation pulse.

Figure 2 shows the flatband shifts as a function of dose, with  $\Delta V_{\text{FB}}$  normalized by the fractional charge yield,  $f(E)$ , from figure 1, and the geometric oxide-thickness dependence. The data points indicate a linear variation of normalized  $\Delta V_{\text{FB}}$  with dose up to  $\sim 10^5$  rad( $\text{SiO}_2$ ).

In the second experiment, HAC MOS samples were subjected to high-dose multiple-pulse irradiation (up to 5 pulses at a rate of 60/s; typically  $1.75 \times 10^5$  rad( $\text{SiO}_2$ ) per pulse). HAC n-type samples were biased at 5, 10, and 20 V during irradiation, while HAC p-type samples were biased at the corresponding negative biases. Flatband shifts were measured at 1 and 12 ms after each radiation pulse. The results are plotted in figure 3. The dashed lines represent the predicted flatband shift based on equation (5) for  $f(E) = 1.0$ . Above  $10^5$  rad( $\text{SiO}_2$ ) the flatband shift evidently ceases to increase linearly with dose. Under negative bias in particular,  $\Delta V_{\text{FB}}$  saturates strongly at a value near the magnitude of the applied bias voltage. Under positive bias,  $\Delta V_{\text{FB}}$  continues to increase with dose, but at a sublinear rate. These experimental results are in qualitative agreement with the observations of Nielsen and Nichols,<sup>11</sup> who measured charge buildup at 90 K under cobalt-60 irradiation.

In the third experiment, the flatband shift in HAC n-type MOS capacitors was observed as a function of time up to 800 s after multiple-pulse irradiations to total doses from 40 to 875 krad( $\text{SiO}_2$ ) and at bias voltages from 5 to 20 V. Typical results are plotted in figure 4. The observed early (4 ms) flatband shifts conform well to predictions of the initial shift based on equation (5). Also, the shift observed following a single 40-krad ( $\text{SiO}_2$ ) pulse (curve E) shows little change with time. At higher doses--150 krad( $\text{SiO}_2$ ) and above--significant decay of the flatband shift occurs, particularly at the higher bias voltages.

<sup>11</sup>R. L. Nielsen and D. K. Nichols, IEEE Trans. Nucl. Sci. NS-20, No. 6, 319 (1973).

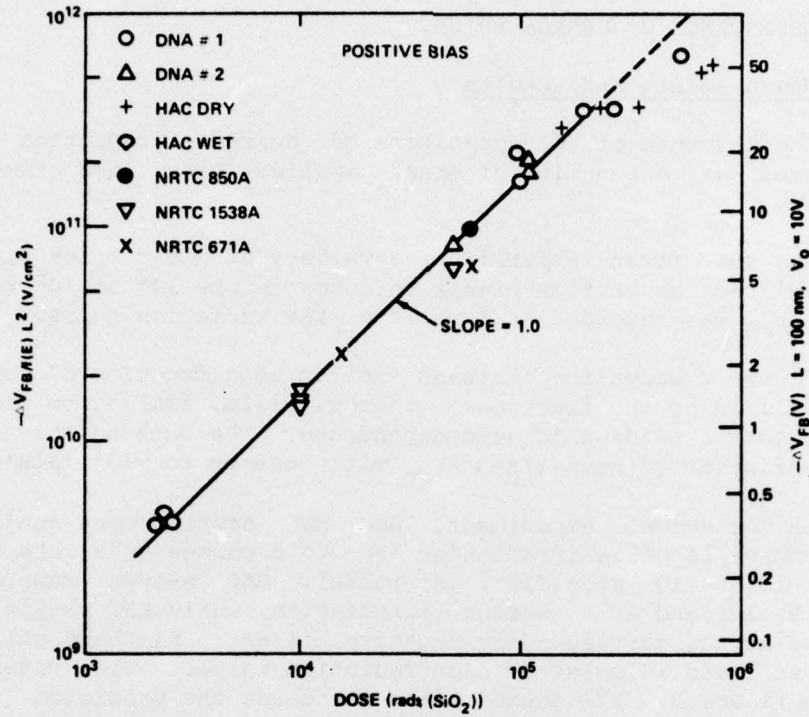


Figure 2. Normalized flatband-voltage shift (left scale) and equivalent flatband shift for  $E = 1$  MV/cm and  $L = 100$  nm for various MOS capacitors at 80 K.

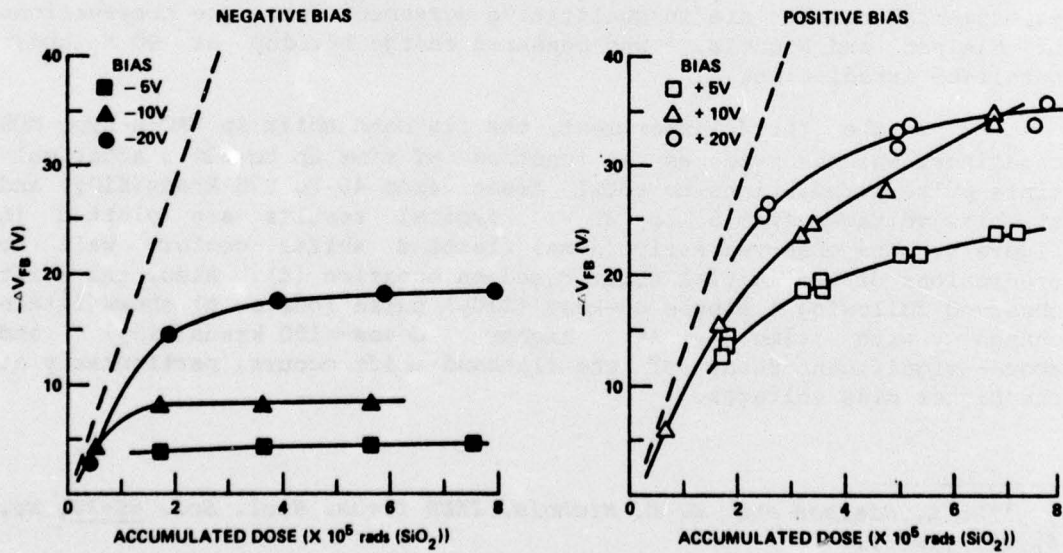


Figure 3. Flatband-voltage shift,  $\Delta V_{FB}$ , 1 ms after irradiation of HAC p-type (left) and n-type (right) MOS capacitors at 80 K.

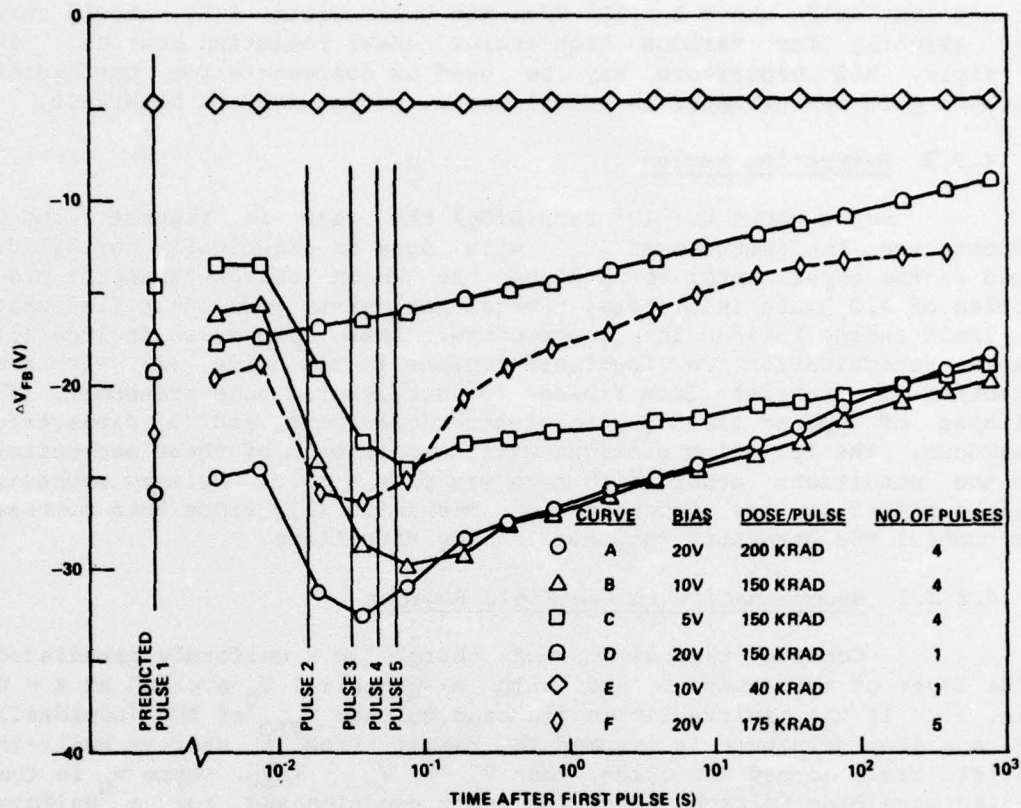


Figure 4. Flatband-voltage shift,  $\Delta V_{FB}$ , as function of time after first LINAC pulse delivered to HAC dry-n MOS capacitors. Samples received multiple pulses at 60 pulses/s (see legend).

## 4.2 Discussion

### 4.2.1 Linear Region

The  $\Delta V_{FB}$  dose-dependence results presented in figure 2 indicate that, below  $\sim 10^5$  rads( $\text{SiO}_2$ ), the charge buildup in a variety of  $\text{SiO}_2$  samples is properly predicted by equation (5). The 80-K shifts are again shown to be large ( $\sim -10$  V at  $10^5$  rads( $\text{SiO}_2$ ) for 100-nm oxide) and independent of sample source and processing details. This uniform  $\Delta V_{FB}$  response to pulsed radiation at low temperatures obtained with an early C-V measurement suggests that such capacitors be used as absolute dosimeters. Simply inverting equation (5) yields

$$D = 5.57 \times 10^{-7} \Delta V_{FB+} / f(E) L^2 \quad (11)$$

For applied fields above  $2 \times 10^6$  V/cm the hole yield  $f(E)$  should vary only slightly for various high-energy (MeV) radiation sources. In principle, MOS capacitors may be used as dosimeters for performing absolute dose measurements in actual device geometries and materials.

#### 4.2.2 Saturation Region

Above about  $2 \times 10^5$  rads( $\text{SiO}_2$ ) the data in figures 2 and 3 indicate that the increase of  $\Delta V_{FB}$  with dose is drastically curtailed. Based on the experimental results and the known charge-transport properties of  $\text{SiO}_2$  gate insulators, several mechanisms were identified that can limit charge buildup in MOS structure. These processes include (1) charge recombination in low-field regions in the oxide, (2) electron injection at high-interface fields, (3) accelerated hole transport, (4) collapse of applied field due to electron transport, and (5) dielectric breakdown. The following sections will discuss each of these mechanisms and the conditions under which each may play a role. Primary emphasis will be placed on the recombination mechanism (1), since this process may control MOS structure response in many situations.

##### 4.2.2.1 Recombination in Low-Field Regions

Consider the buildup of charge in a uniformly irradiated oxide layer of thickness  $L$  and with a potential  $V_0$  applied at  $x = 0$  (fig. 5). If the preirradiation flatband voltage  $V_{FBO}$  of the (nonideal) MOS capacitor structure is assumed to result from a uniform built-in electric field across the oxide, then  $V_0 = V_G - V_{FBO}$ , where  $V_G$  is the applied gate bias voltage. From Poisson's equation and for a uniform charge buildup, the electric field in the oxide is given by

$$E(x) = \rho/\epsilon (x - L/2) + V_0/L \quad . \quad (12)$$

For  $\rho < |2\epsilon V_0/L^2|$ , corresponding to  $|\Delta V_{FB}| < |V_0|$ , the electric field in the oxide is monotonic and the radiation-generated electrons are quickly swept out without interacting with the stationary holes (fig. 5a). Note, however, that the electric field is increasing at  $x = L$  and decreasing at  $x = 0$  because of the contribution of the hole space-charge field. At a critical dose  $D_{sat}$ ,  $\rho$  approaches  $|2\epsilon V_0/L^2|$  (corresponding to the magnitude of the flatband shift approaching the magnitude of the applied potential), and the electric field at  $x = 0$  reaches zero and tries to go negative (fig. 5b). In this case, the electrons being swept toward  $x = 0$  come to a virtual halt in the zero field region and undergo efficient recombination with the holes in the vicinity. The result is that the hole density near  $x = 0$  is rapidly wiped out. As irradiation of the oxide continues (fig. 5c), the zero point for the electric field and, consequently, the zone of rapid recombination move deeper into the

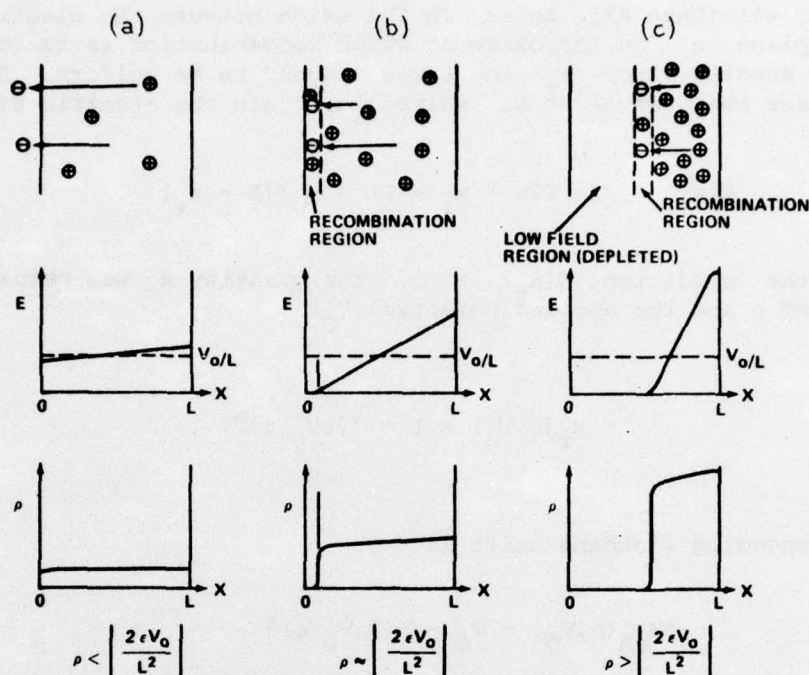


Figure 5. Model for limitation of charge buildup in an oxide layer: (a) electron sweepout; (b) recombination at the interface; (c) recombination in oxide interior.

oxide, "eating away" at the hole distribution. The oxide charge and the total electric field continue to increase at  $x = L$ . For irradiation under positive bias,  $x = 0$  in figure 5 corresponds to the electrode interface and  $x = L$  is the Si interface. In this case, the recombination process reduces the hole density in a region well removed from the Si interface; consequently,  $\Delta V_{FB+}$  continues to increase as a function of dose following the onset of recombination, but begins to saturate. For irradiation under negative bias,  $x = 0$  in figure 5 corresponds to the Si interface, and the onset of recombination drastically affects any further increase in  $\Delta V_{FB-}$  with added dose. In fact, since the net electric field at the Si interface is pinned at zero for  $\rho \geq |2\epsilon V_0/L^2|$ , the flatband shift under negative bias is similarly pinned to  $\Delta V_{FB-} = V_0$ . The derivation of the expected dependence on dose of the flatband shift,  $\Delta V_{FB+}$  under positive bias, was based on this simple model for limiting by recombination and also on certain assumptions. At a given dose above  $D_{sat}$  the recombination process is

assumed to eliminate all holes in the oxide between the electrode ( $x = 0$ ) and a plane  $x_r$  in the oxide at which recombination is taking place. The hole density  $r$  from  $x_r$  to  $L$  was assumed to be uniform. Poisson's equation for this situation was solved to obtain the electric field:

$$E(x) = \rho/2\epsilon (2x - x_r - L) + V_0/(L - x_r) . \quad (13)$$

Imposing the condition  $E(x_r) = 0$ , the quantity  $x_r$  was obtained as a function of  $\rho$  and the applied potential  $V_0$ :

$$x_r(\rho, V_0) = L - (2\epsilon V_0/\rho)^{1/2} . \quad (14)$$

The corresponding flatband shift is

$$\begin{aligned} \Delta V_{FB}(\rho, V_0) &= V_0 - L(2\rho V_0/\epsilon)^{1/2} \\ \text{for } |\Delta V_{FB+}| &> |V_0| . \end{aligned} \quad (15)$$

Using equation (4), we may express  $\Delta V_{FB}$  as a function of oxide dose:

$$\begin{aligned} \Delta V_{FB+}(D, V_0) &= V_0 - 2.68 \times 10^3 L [V_0 f(E) D]^{1/2} \\ \text{for } |\Delta V_{FB+}| &> |V_0| . \end{aligned} \quad (16)$$

This relationship predicts, therefore, that the flatband shift will increase with the square root of the dose for total flatband shifts greater than the applied potential.

The simple recombination model did not include such factors as the field dependence of charge yield in the oxide and the initial displacement of the holes. To aid in a more careful analysis of the  $\Delta V_{FB}$  limitation mechanisms, a computer program was written to simulate the charge-buildup process in a basic MOS structure. This

program repetitively solved Poisson's equation in the  $x$  dimension as electron-hole pairs were generated in the oxide to obtain the charge and electric field distribution across the oxide layer as a function of time and dose. The generation rate for electron-hole pairs in each  $x$  subinterval was governed by the instantaneous electric field in that interval through the experimental yield/field relationship in figure 1. The program allowed for initial displacement of the holes according to the schubweg model, following which the holes were assumed to be immobile. In keeping with the discussion above, the electrons were assumed to be infinitely mobile; that is, they move without limit unless stopped at a point of field reversal. Hole-electron recombination was allowed only at field reversal points.

Representative results from this computer model are shown in figure 6. No parameters were adjusted to obtain these results; all the constants used in the calculation were derived from material properties and the data in figure 1 and table II. Field and hole density profiles in the oxide are shown for doses to  $10^6$  rads( $\text{SiO}_2$ ) for an 87.5-nm oxide under 10-V bias (HAC dry  $n$  or  $p$ ). Note the apparent concentration of the hole buildup and, consequently, the electric field near the  $x = L$  interface (Si interface under positive bias) as the dose increases. Other workers have also found evidence for concentration of the holes near the Si interface under positive bias at low temperature.<sup>11,12</sup> It is important to recognize that bunching of the holes near the interface at low temperature does not require hole transport or preferential trapping in that region, but results from the progressive elimination of holes in the balance of the oxide.

Both the simple model and computer model predictions for the flatband shifts in the HAC samples as a function of dose under negative and positive bias are compared in figure 7. Also plotted are the experimental  $\Delta V_{\text{FB}}$  data from figure 3 (points). Both the simple recombination model and the computer simulation results reproduce the sharp limitation of  $\Delta V_{\text{FB}}$  to essentially the applied negative bias. The computer calculation shows a stronger limitation of the positive bias shift than predicted by the simple analytic model; this is primarily a result of hole loss by initial transport which becomes significant as the electric field near the Si interface increases and the hole region shrinks. The 5- and 10-V computer-model curves agree with the

<sup>11</sup>R. L. Nielsen and D. K. Nichols, *IEEE Trans. Nucl. Sci.* **NS-20**, No. 6, 319 (1973).

<sup>12</sup>E. Harari, S. Wang, and B. S. H. Royce, *J. Appl. Phys.* **46**, 1310 (1975).

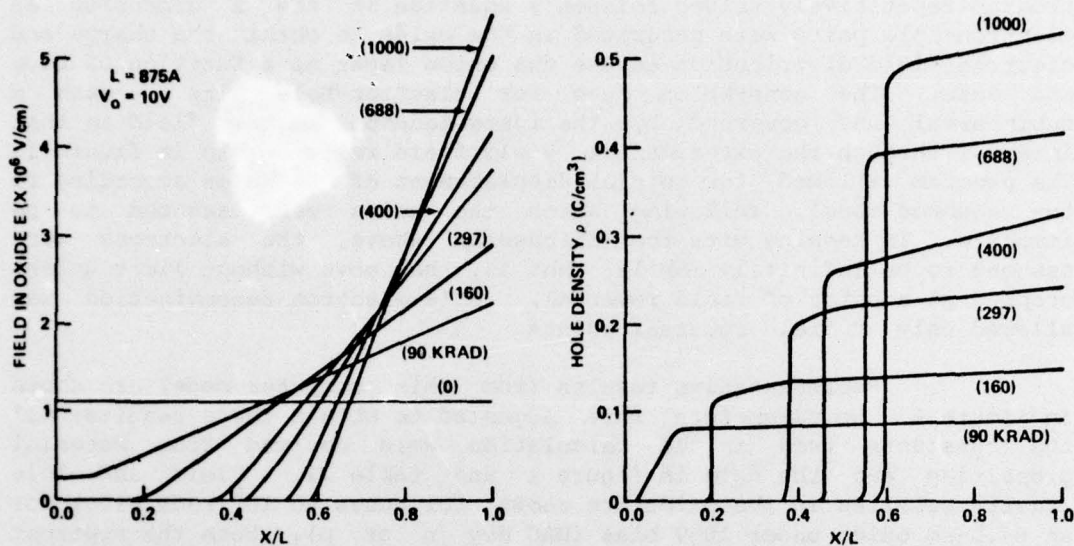


Figure 6. Calculated field and hole density profiles in the oxide as a function of dose at 80 K.

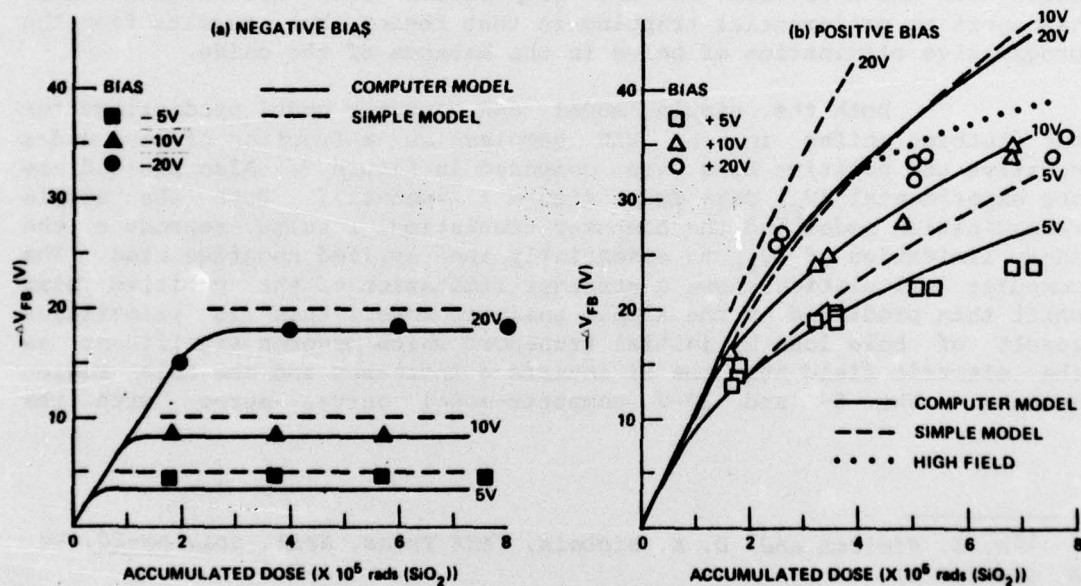


Figure 7. Comparison of model calculations and experimental results on the flatband-voltage shift under (a) positive and (b) negative bias at 80 K.

experimental results, indicating that the recombination mechanism accounts for most of the charge-buildup limitation in these cases. The 20-V bias data points show strong  $\Delta V_{FB}$  saturation above  $5 \times 10^5$  rads( $\text{SiO}_2$ ) which is not predicted by the computer model; evidently other processes, which will be discussed further, contribute to buildup limitation in this case.

#### 4.2.2.2 Electron Injection at High Fields

The computer simulation of the 20-V buildup predicted that the total electric field at the Si interface should have increased beyond  $5 \times 10^6$  V/cm for doses above  $3 \times 10^5$  rads( $\text{SiO}_2$ ), while the field in the 10-V case was predicted to remain below that value to above  $8 \times 10^5$  rads( $\text{SiO}_2$ ). Mitchell<sup>13</sup> noted that high interface fields would be expected to cause injection of electrons into the oxide from the silicon which would in time result in elimination of some holes in the oxide by recombination. Powell<sup>14</sup> measured significant electron injection via tunneling for interface fields greater than  $6 \times 10^6$  V/cm. Since the tunneling current increased exponentially with the field, this process could result in a strong saturation of the flatband shift above a critical value. A crude attempt at including the electron injection process in the computer model yielded results (dotted line, fig. 7b) in reasonable agreement with the experimental data.

If it is assumed that a mechanism such as tunneling limits the interface field to  $E(L) = E_{\max}$ , then the maximum flatband shift which can be obtained is

$$\Delta V_{FB+} = V_0 - LE_{\max} \quad (17)$$

The dose at which this flatband shift is first attained may be estimated from the analytic recombination model introduced earlier. Substituting equation (14) into equation (13), setting  $E(L) = E_{\max}$  and rearranging,

$$\rho(E_{\max}, V_0) = \epsilon E_{\max}^2 / 2V_0 \quad (18)$$

or, applying equation (4),

$$D_{\text{sat}} = 1.39 \times 10^{-7} E_{\max}^2 / f(E) V_0 \quad (19)$$

<sup>13</sup>J. P. Mitchell, *IEEE Trans. Elec. Dev.* ED-14, No. 11, 764 (1967).

<sup>14</sup>R. J. Powell, *IEEE Trans. Nucl. Sci.* NS-22, 2240 (1975).

For an 87.5-nm oxide biased at 20 V and  $E_{\max} = 6.5 \times 10^6$  V/cm, the saturation shift of -37 V should be attained at  $3.7 \times 10^5$  rads( $\text{SiO}_2$ ). For 5-V bias under similar conditions,  $\Delta V_{\text{FB}+} = -52$  V at  $D_{\text{sat}} = 1.9 \times 10^6$  rads( $\text{SiO}_2$ ). Thus, field limiting is much more likely to occur at higher applied voltage.

#### 4.2.2.3 Hole Transport

As noted previously, figure 4 shows that significant decay of  $\Delta V_{\text{FB}}$  occurs at 80 K for pulsed irradiation of  $\text{SiO}_2$  samples to doses above 150 krad( $\text{SiO}_2$ ). As plotted,  $\Delta V_{\text{FB}}$  for most of the samples decreases linearly as a function of  $\log t$  (time). This logarithmic flatband shift decay is typical of hole loss by transport through the oxide.<sup>1</sup> Although the discussion thus far has assumed that the holes (after an initial displacement) are essentially immobile near 80 K, hole motion is greatly accelerated at higher fields.<sup>4</sup> The curves in figure 4 show evidence that the rate of  $\Delta V_{\text{FB}}$  decay is bias dependent: the shift with 10-V applied, shown in curve B (four pulses of 150 krad each) decays more rapidly than the corresponding 5-V shift (curve C); the 20-V shift for one 150-krad pulse (curve D) although initially smaller, decays even more rapidly. If the decay were due to electron injection, the samples biased at 20 V which received multiple pulses should show much more rapid charge loss since the space-charge contribution to the interface field is greater; however, this was not observed (except in the sample that received five 175-krad pulses (curve F), which will be discussed). The charge-loss mechanism here is therefore believed to be field-activated hole transport at the moderately high ( $2.3 \times 10^6$  V/cm) field present across the oxide.

The sample exposed to five 175-krad pulses at 20-V bias (fig. 4, curve F) shows relatively rapid charge loss which slows down in about a minute. This sample was exposed to the radiation pulses while mounted in an evacuated sample holder maintained at 80 K. The only mechanisms for removing heat from the sample were radiation to the 80-K surroundings (negligible at low temperature) and direct thermal conduction along the two header lead wires to the socket. It is therefore likely that this sample underwent essentially lossless heating when subjected to 875 krad( $\text{SiO}_2$ ) in 67 ms. The temperature rise was estimated to be ~60 K from the low-temperature heat capacity of the

<sup>1</sup>H. E. Boesch, Jr., F. B. McLean, J. M. McGarrity, and G. A. Ausman, Jr., *IEEE Trans. Nucl. Sci.* **NS-22**, 2163 (1975).

<sup>4</sup>F. B. McLean, H. E. Boesch, Jr., and J. M. McGarrity, *Hole Transport and Recovery Characteristics of MOS Gate Insulators*, *IEEE Nuclear and Space Radiation Effects Conference*, July 1976.

silicon substrate and the header material. At  $\sim 140$  K, hole transport is greatly accelerated compared to its rate at 80 K. While this mechanism does not strictly apply to devices operated at 80 K, the possibility that devices may undergo significant transient heating in a real radiation environment should not be ignored.

#### 4.2.2.4 Collapse of Applied Field

Another mechanism that may limit oxide-charge buildup in devices operated in pulsed nuclear environments is collapse of the bias voltage applied across the oxide during a radiation pulse. Since the radiation-generated electrons are mobile, their motion through the oxide under the applied field constitutes a current which may discharge the gate-substrate capacitance,  $C$ . If the circuit that consists of the internal resistances of the device and any series external elements has an equivalent series resistance  $R$  such that  $RC$  is greater than the duration of the radiation pulse  $\tau$ , the bias on the device will collapse during a radiation pulse of sufficient magnitude. For  $RC > \tau$ , the fractional charge loss on  $C$  due to electron movement only is given by

$$\Delta Q/Q = 1/2 \rho A L / C V_G = \rho L^2 / 2 \epsilon V_G \quad (20)$$

where  $A$  is the oxide area and  $Q$  is the charge on the capacitor. The dose  $D$  at which complete field collapse (discharge, corresponding to  $\Delta Q/Q \sim 1$ ) should first occur, may be obtained through application of equation (4):

$$D_{\text{sat}} \sim 6 \times 10^{-7} V_G / f(E) L^2 \quad (21)$$

The corresponding saturation flatband shift is equal to the magnitude of the applied voltage:

$$|\Delta V_{\text{FB}}(D_{\text{sat}})| \sim |-V_G| \quad (22)$$

#### 4.2.2.5 Dielectric Breakdown

Another mechanism may operate if the ones discussed so far fail to limit charge buildup in an MOS structure or if weaknesses exist in that structure. During the course of the experiments, a few MOS capacitors short-circuited under test, usually after receiving a high dose (greater than  $3 \times 10^5$  rads( $\text{SiO}_2$ )) and following irradiation at  $V_G \geq 20$  V. Yang, Johnson, and Lampert<sup>15</sup> have investigated a self-enhanced breakdown mechanism in which electrons tunneling into the  $\text{SiO}_2$  in high-field regions become "hot" and generate holes by impact ionization, thereby enhancing the local field and therefore the tunneling current. A sudden increase in interface field due to holes generated in the oxide by a radiation pulse may trigger this failure mechanism in an MOS structure with oxide defects (near-pinholes) which cause local field concentration. In complex devices such as LSI logic and CCD's, the device geometry (e.g., metallization pattern) may cause field concentration in small areas, leading to device burnout.

#### 4.2.2.6 Applicability to Higher Temperatures

It should be noted that most of the flatband-shift limitation processes which have been discussed are not inherently restricted to situations in which the device is irradiated at low temperature. With the exception of the hole-transport processes, the modeling and conclusions presented are valid for any situation in which little hole motion takes place during the radiation pulse. The data of Hughes et al<sup>3</sup> and Srour et al<sup>10</sup> indicate that little hole motion occurs in less than  $10^{-8}$  s even at room temperature. Therefore, most of the processes discussed should limit the initial shift for room temperature irradiations in most pulsed nuclear and flash x-ray environments. At room temperature, rapid charge removal by hole transport ("short-term annealing") takes place within seconds after irradiation.<sup>1</sup> The flatband or threshold shift remaining after transport is presumably determined by the highly processing-dependent density of deep-hole traps in the oxide which capture some of the transported holes. Consequently, any process which limits the initial shift should cause a proportionate reduction in the shift remaining at late time.

---

<sup>1</sup>H. E. Boesch, Jr., F. B. McLean, J. M. McGarrity, and G. A. Ausman, Jr., *IEEE Trans. Nucl. Sci.* NS-22, 2163 (1975).

<sup>3</sup>R. C. Hughes, E. P. Eer Nisse, and H. J. Stein, *IEEE Trans. Nucl. Sci.* NS-22, 2227 (1975).

<sup>10</sup>J. R. Srour, O. L. Curtis, Jr., and K. Y. Chiu, *IEEE Trans. Nucl. Sci.* NS-21, No. 6, 73 (1974).

<sup>15</sup>W. C. Johnson, *IEEE Trans. Nucl. Sci.* NS-22, 2144 (1975).

## 5. CONCLUSIONS

The yield of holes produced in  $\text{SiO}_2$  subjected to high-energy short-pulse radiation at  $\sim 80$  K was measured as a function of electric field, and a hole-electron pair-creation energy of 18 eV was derived. Early differences in  $\Delta V_{\text{FB}}$  under positive and negative biases at 80 K imply an initial hole displacement of  $\sim 9$  nm at  $10^6$  V/cm. The extremely large flatband-voltage shifts attained in MOS structures per unit dose at 80 K were shown to be predictable, processing independent, and linear in dose to  $\sim 10^5$  rads( $\text{SiO}_2$ ). At higher doses the shifts increase sublinearly with dose, primarily as a result of recombination in a low-field region of the oxide. Other mechanisms such as electron injection and hole transport probably play a role as radiation-induced space-charge fields in the oxide become large. The limitation processes should be effective even at room temperature so long as little hole transport takes place during irradiation.

## ACKNOWLEDGEMENTS

The authors thank R. Severance and E. Ross of the AFRRI LINAC staff for their beyond-the-call efforts during the experiment and F. B. McLean and G. A. Ausman, Jr., for many helpful discussions. The technical assistance of K. C. Hall is gratefully acknowledged.

## LITERATURE CITED

- (1) H. E. Boesch, Jr., F. B. McLean, J. M. McGarrity, and G. A. Ausman, Jr., IEEE Trans. Nucl. Sci. NS-22, 2163 (1975).
- (2) H. H. Sander and B. L. Gregory, IEEE Trans. Nucl. Sci. NS-22, 2157 (1975).
- (3) R. C. Hughes, E. P. Eer Nisse, and H. J. Stein, IEEE Trans. Nucl. Sci. NS-22, 2227 (1975).
- (4) F. B. McLean, H. E. Boesch, Jr., and J. M. McGarrity, Hole Transport and Recovery Characteristics of MOS Gate Insulators, IEEE Nuclear and Space Radiation Effects Conference (July 1976).
- (5) G. A. Ausman, Jr., and F. B. McLean, Appl. Phys. Lett. 26, 173 (1975).
- (6) H. E. Boesch, Jr., Development of Apparatus for Performing Rapid Capacitance-Voltage Measurements on MIS Structures, Harry Diamond Laboratories TM-76-33 (December 1976).

LITERATURE CITED (Cont'd)

- (7) F. B. McLean, H. E. Boesch, Jr., P. S. Winokur, J. M. McGarrity, and R. B. Oswald, Jr., IEEE Trans. Nucl. Sci. NS-21, 47 (1974).
- (8) O. L. Curtis, Jr., J. R. Srour, and K. Y. Chiu, J. Appl. Phys. 45, 4506 (1974).
- (9) R. E. Leadon, D. P. Snowden, and J. M. Wilkenfeld Radiation Effects in Semiconductor and Insulator Materials, IRT Corporation, Harry Diamond Laboratories CR-76-152-1 (April 1976).
- (10) J. R. Srour, O. L. Curtis, Jr., and K. Y. Chiu, IEEE Trans. Nucl. Sci. NS-21, No. 6, 73 (1974).
- (11) R. L. Nielsen and D. K. Nichols, IEEE Trans. Nucl. Sci. NS-20, No. 6, 319 (1973).
- (12) E. Harari, S. Wang, and B. S. H. Royce, J. Appl. Phys. 46, 1310 (1975).
- (13) J. P. Mitchell, IEEE Trans. Elec. Dev. ED-14, No. 11, 764 (1967).
- (14) R. J. Powell, IEEE Trans. Nucl. Sci. NS-22, 2240 (1975).
- (15) W. C. Johnson, IEEE Trans. Nucl. Sci. NS-22, 2144 (1975).

# DISTRIBUTION

DEFENSE DOCUMENTATION CENTER  
CAMERON STATION, BUILDING 5  
ALEXANDRIA, VA 22314  
ATTN DDC-TCA (12 COPIES)

COMMANDER  
USA RSCH & STD GP (EUR)  
BOX 65  
FPO NEW YORK 09510  
ATTN LTC JAMES M. KENNEDY, JR.  
CHIEF, PHYSICS & MATH BRANCH

COMMANDER  
US ARMY MATERIEL DEVELOPMENT  
& READINESS COMMAND  
5001 EISENHOWER AVENUE  
ALEXANDRIA, VA 22333  
ATTN DRXAM-TL, HQ TECH LIBRARY  
ATTN DRCDE, DIR FOR DEV & ENGR  
ATTN DRCDE-R, SYS EVAL & TESTING  
ATTN DRCSE-N, NUCLEAR  
ATTN DRCDE-D, LAWRENCE FLYNN

COMMANDER  
USA ARMAMENT COMMAND  
ROCK ISLAND, IL 61201  
ATTN DRSAR-ASF, FUZE DIV  
ATTN DRSAR-RDF, SYS DEV DIV - FUZES  
ATTN DRSAR-SC, CHIEF SCIENTIST

COMMANDER  
USA MISSILE & MUNITIONS CENTER  
& SCHOOL  
REDSTONE ARSENAL, AL 35809  
ATTN ATSK-CTD-F

ARGONNE NATIONAL LABORATORY  
9700 SOUTH CASS AVE  
ARGONNE, IL 60439

BROOKHAVEN NATIONAL LABORATORY  
ASSOCIATED UNIVERSITIES, INC.  
UPTON, LONG ISLAND, NY 11973

US DEPARTMENT OF COMMERCE  
ASSISTANT SECRETARY FOR SCIENCE  
& TECHNOLOGY  
WASHINGTON, DC 20230

US ENERGY RESEARCH & DEVELOPMENT  
ADMINISTRATION  
WASHINGTON, DC 20545  
ATTN ASST ADMIN FOR NUCLEAR ENERGY  
ATTN DIV OF SPACE NUCLEAR SYSTEMS  
ATTN DIV OF REACTOR RES & DEV

US ENERGY RESEARCH & DEVELOPMENT  
ADMINISTRATION  
ALBUQUERQUE OPERATIONS  
P.O. BOX 5400  
ALBUQUERQUE, NM 87115  
ATTN DOCUMENT CONTROL FOR WSSB

US ENERGY RESEARCH & DEVELOPMENT  
ADMINISTRATION  
TECHNICAL INFORMATION ORGANIZATION  
P.O. BOX 62  
OAK RIDGE, TN 37830

DIRECTOR  
ARMED FORCES RADIOBIOLOGY RESEARCH  
INSTITUTE  
DEFENSE NUCLEAR AGENCY  
NATIONAL NAVAL MEDICAL CENTER  
BETHESDA, MD 20014  
ATTN R. WEISS, CPT.

DIRECTOR  
DEFENSE ADVANCED RESEARCH  
PROJECTS AGENCY  
ARCHITECT BLDG  
1400 WILSON BLVD  
ARLINGTON, VA 22209  
ATTN DIR, MATERIAL SCIENCES  
ATTN TECH INFO OFFICE  
ATTN DIR, STRATEGIC TECHNOLOGY OFFICE  
ATTN DIR, TECHNOLOGY  
ASSESSMENTS OFFICE

DEFENSE COMMUNICATION ENGINEER CENTER  
1860 WIEHLE AVENUE  
RESTON, VA 22090  
ATTN CODE R320, C. W. BERGMAN  
ATTN CODE R410, JAMES W. MCLEAN  
ATTN RES & DEV

DIRECTOR  
DEFENSE COMMUNICATIONS AGENCY  
WASHINGTON, DC 20305  
ATTN CODE 930, MONTE I. BURGETT, JR  
ATTN CODE 540.5  
ATTN TECH LIBRARY

DIRECTOR  
DEFENSE INTELLIGENCE AGENCY  
WASHINGTON, DC 20301  
ATTN DS-4A2

DIRECTOR  
DEFENSE NUCLEAR AGENCY  
WASHINGTON, DC 20305  
ATTN DDST  
ATTN RAEV (3 COPIES)  
ATTN STTL TECH LIBRARY  
ATTN STVL  
ATTN RATN  
ATTN PETER HAAS, DEP DIR,  
SCI TECHNOLOGY  
ATTN AEROSPACE SYS DIR (SPAS)  
ATTN VULNERABILITY DIRECTORATE

DIRECTOR  
DEFENSE COMMUNICATIONS AGENCY  
NATIONAL MILITARY COMMAND  
SYSTEM SUPPORT CENTER  
WASHINGTON, DC 20301  
ATTN TECHNICAL DIRECTOR (B102)

DIR OF DEFENSE RSCH & ENGINEERING  
DEPARTMENT OF DEFENSE  
WASHINGTON, DC 20301  
ATTN DD/S&SS  
ATTN DD/S&AS  
ATTN AD/E&PS  
ATTN DEP DIR (TEST & EVALUATION)  
ATTN DEP DIR (RES & ADVANCED TECH)

COMMANDER  
FIELD COMMAND  
DEFENSE NUCLEAR AGENCY  
KIRTLAND AFB, NM 87115  
ATTN FCPRL

DIRECTOR  
INTERSERVICE NUCLEAR WEAPONS SCHOOL  
KIRTLAND AFB, NM 87115  
ATTN DOCUMENT CONTROL

DIRECTOR  
JOINT STRATEGIC TARGET PLANNING STAFF,  
JCS  
OFFUTT AFB  
OMAHA, NB 68113  
ATTN JLTW-2

CHIEF  
LIVERMORE DIVISION, FIELD COMMAND DNA  
LAWRENCE LIVERMORE LABORATORY  
P.O. BOX 808  
LIVERMORE, CA 94550  
ATTN FCPRL

DIRECTOR  
NATIONAL SECURITY AGENCY  
FT. GEORGE G. MEADE, MD 20755  
ATTN O. O. VAN GUNTEN, R-425  
ATTN TDL

OFFICE, CHIEF OF RESEARCH, DEVELOPMENT  
& ACQUISITION  
DEPARTMENT OF THE ARMY  
WASHINGTON, DC 20310  
ATTN DAMA-AR, CHIEF SCI, DA & DIR OF  
ARMY RES, DR. M. E. LASSER  
ATTN DAMA-AR, RESEARCH PROGRAMS  
ATTN DAMA-RA, SYS REVIEW & ANALYSIS  
ATTN DAMA-CSS-D, R&D TEAM

BALLISTIC MISSILE DEFENSE PROGRAM  
MANAGER OFFICE  
COMMONWEALTH BUILDING  
1300 WILSON BLVD  
ARLINGTON, VA 22209  
ATTN DACS-BMT, TECHNOLOGY DIR

PROJECT MANAGER  
ARMY TACTICAL DATA SYSTEMS  
US ARMY ELECTRONICS COMMAND  
FORT MONMOUTH, NJ 07703  
ATTN DWAIN B. HUEWE  
ATTN DRCPN-TDS-SD

COMMANDER  
BMD SYSTEM COMMAND  
PO BOX 1500  
HUNTSVILLE, AL 35807  
ATTN BDMSC-TEN, NOAH J. HURST  
ATTN BMDSC-T, TEST & SYS ENGR SUP DIR

COMMANDER  
BALLISTIC MISSILE DEFENSE ADVANCED  
TECHNOLOGY CENTER  
PO BOX 1500  
HUNTSVILLE, AL 35807  
ATTN DIRECTOR, ATC-X  
ATTN TECH LIB

COMMANDER  
US ARMY COMMUNICATIONS COMMAND  
FORT HUACHUCA, AZ 85613  
ATTN TECH LIB

COMMANDER  
US ARMY COMPUTER SYS COMMAND  
FORT BELVOIR, VA 22060  
ATTN TECH LIB

COMMANDER  
US ARMY ELECTRONICS COMMAND  
FORT HOLABIRD, MD 21219

PROJECT MANAGER, SAM-D  
US ARMY MATERIEL DEV &  
READINESS COMMAND  
REDSTONE ARSENAL, AL 35809

US ARMY MISSILE RESEARCH, DEV, &  
ENGINEERING LABORATORY  
US ARMY MISSILE COMMAND  
REDSTONE ARSENAL, AL 35809  
ATTN DRSMI-RF, ADV SYS CONCEPTS OFC  
ATTN DRSMI-RG, GUIDANCE & CONTROL  
ATTN DRSMI-RE, ADVANCED SENSORS DIR

# DISTRIBUTION (Cont'd)

COMMANDER  
FRANKFORD ARSENAL  
BRIDGE AND TACONY STREETS  
PHILADELPHIA, PA 19137  
ATTN SARFA-PCD, MARVIN ELNICK  
ATTN A1000, TECH DIR

COMMANDING OFFICER  
NIGHT VISION LABORATORY  
U. S. ARMY ELECTRONICS COMMAND  
FORT BELVOIR, VA 22060  
ATTN CAPT ALLAN S. PARKER  
ATTN TECHNICAL LIBRARY

COMMANDER  
PICATINNY ARSENAL  
DOVER, NJ 07801  
ATTN SARPA-ND-D-B, EDWARD J. ARBER  
ATTN SARPA-ND-W  
ATTN SARPA-ND-N  
ATTN SARPA-FR-E, LOUIS AVRAMI  
ATTN SARPA-FR-S-P  
ATTN SARPA-TS-S, SCI & TECH INFO DIV  
ATTN SARPA-ND-N-E

COMMANDER  
REDSTONE SCIENTIFIC INFORMATION CTR  
US ARMY MISSILE COMMAND  
REDSTONE ARSENAL, AL 35809  
ATTN CHIEF, DOCUMENTS

SECRETARY OF THE ARMY  
WASHINGTON, DC 20310  
ATTN ODUSA OR DANIEL WILLIARD

ASSISTANT SECRETARY OF THE ARMY (R&D)  
WASHINGTON, DC 20310  
ATTN DEP FOR SCI & TECH

COMMANDER  
TRASANA  
WHITE SANDS MISSILE RANGE, NM 88002  
ATTN ATAA-EAC, FRANCIS N. WINANS

DIRECTOR  
US ARMY BALLISTIC RESEARCH LABORATORIES  
ABERDEEN PROVING GROUND, MD 21005  
ATTN DAVID L. RIGOTTI, DRXBR-BVL  
ATTN DRXBR-X, JULIUS J. MESZAROS  
ATTN DRXBR-AM, W. R. VANANTWERP  
ATTN DRXBR-VL, JOHN W. KINCH  
ATTN DRXBR-VL, ROBERT L. HARRISON

CHIEF  
US ARMY COMMUNICATIONS SYSTEMS AGENCY  
FORT MONMOUTH, NJ 07703  
ATTN SCCM-AD-SV (LIBRARY)

COMMANDER  
US ARMY ELECTRONICS COMMAND  
FORT MONMOUTH, NJ 07703  
ATTN DRSEL-CT-HDK, ABRAHAM E. COHEN  
ATTN DRSEL-TL-MD, GERHART K. GAULE  
ATTN DRSEL-GG-TD, W. R. WERK  
ATTN DRSEL-PL-ENV, HANS A. BOMKE  
ATTN DRSEL-TL-ND, S. KRONENBEY  
ATTN DRSEL-TL-IR, EDWIN T. HUNTER  
ATTN DRSEL-TL-EN, ROBERT LUX  
ATTN DRSEL-CE, T. PREIFFER  
ATTN DRSEL-RD, DIR, RES, DEV, & ENGR  
ATTN DRSEL-WL-D, ELECTE WARFARE LAB  
ATTN DRSEL-VL-D, AVIONICS LAB  
ATTN DRSEL-TL-D, ELECTRONICS  
TECHNOLOGY & DEVICES LAB

COMMANDANT  
US ARMY ENGINEER SCHOOL  
FT. BELVOIR, VA 22060

COMMANDER-IN-CHIEF  
US ARMY EUROPE AND SEVENTH ARMY  
APO NEW YORK 09403  
ATTN ODCSE-E, AEAGE-PI

COMMANDANT  
U.S. ARMY FIELD ARTILLERY SCHOOL  
FORT SILL, OK 73503  
ATTN ATSPA-CTD-ME, HARLEY MOBERG

COMMANDER  
US ARMY MISSILE COMMAND  
REDSTONE ARSENAL  
HUNTSVILLE, AL 35809  
ATTN DRCPM-PE-EA, WALLACE O. WAGNER  
ATTN DRSI-RGP, VICTOR W. RUWE  
ATTN DRSMI-RRR, FAISON P. GIBSON  
ATTN DRCPM-MDTI, CPT JOE A. SIMS  
ATTN DRCPM-LCEX, HOWARD H. HENRIKSEN  
ATTN DRSMI-RGP, HUGH GREEN  
ATTN ARMY MISSILE RDE LAB  
ATTN TECH LIB

COMMANDER  
US ARMY MOBILITY EQUIP R&D CTR  
FORT BELVOIR, VA 22060  
ATTN STSFB-MW, JOHN W. BOND, JR.

CHIEF  
US ARMY NUC AND CHEMICAL SURETY GP  
BLDG, 2073, NORTH AREA  
FT. BELVOIR, VA 22060  
ATTN MOSG-ND, MAJ SIDNEY W. WINSLOW

COMMANDER  
US ARMY NUCLEAR AGENCY  
FORT BLISS, TX 79916  
ATTN ATCN-W, LTC LEONARD A. SLUGA

COMMANDER  
U.S. ARMY TANK AUTOMOTIVE COMMAND  
WARREN, MI 48090  
ATTN DRCPM-GCM-SW, LYLE A. WOLCOTT

COMMANDER  
US ARMY TEST AND EVALUATION COMMAND  
ABERDEEN PROVING GROUND, MD 21005  
ATTN DRSTE-EL, R. I. KOLCHIN  
ATTN DRSTE-NB, R. R. GALASSO

COMMANDER  
WHITE SANDS MISSILE RANGE  
WHITE SANDS MISSILE RANGE, NM 88002  
ATTN STEWS-TE-NT,  
MR. MARVIN P. SQUIRES

COMMANDER  
US ARMY NUCLEAR AGENCY  
FORT BLISS, TX 79916  
ATTN ATCN-W, WEAPONS EFFECTS DIV  
ATTN TECH LIB

COMMANDER  
HQ, US ARMY TEST & EVALUATION COMMAND  
ABERDEEN PROVING GROUND, MD 21005  
ATTN DRSTE-EL, ELECTRONICS MATERIEL  
TESTING DIR

COMMANDER  
EDGEWOOD ARSENAL  
EDGEWOOD ARSENAL, MD 21010  
ATTN SAREA-R, RES LABORATORIES  
ATTN SAREA-DE, DIR OF DEV & ENGR  
ATTN SAREA-TS, TECH LIB

OFFICE OF RESEARCH, DEVELOPMENT,  
TEST & EVALUATION  
DEPT OF THE NAVY  
WASHINGTON, DC 20360  
ATTN OF-987, R&D PLANS

US NAVAL ACADEMY  
ENGINEERING DEPT  
ANNAPOLIS, MD 21402  
ATTN LIBRARY

COMMANDER  
NAVAL AIR SYSTEMS COMMAND HQ  
DEPT OF THE NAVY  
WASHINGTON, DC 20360  
ATTN TECHNICAL LIBRARY

COMMANDER  
NAVAL ELECTRONICS LABORATORY CENTER  
SAN DIEGO, CA 92152  
ATTN CODE 6400, TECH INFO DIV

SUPERINTENDANT  
NAVAL POSTGRADUATE SCHOOL  
MONTEREY, CA 93940  
ATTN LIBRARY, CODE 2124

CHIEF OF NAVAL RESEARCH  
NAVY DEPARTMENT  
ARLINGTON, VA 22217  
ATTN CODE 427  
ATTN CODE 421, DORAN W. PADGETT  
ATTN TECHNICAL LIBRARY

COMMANDING OFFICER  
NAVAL AVIONICS FACILITY  
21ST AND ARLINGTON AVENUE  
INDIANAPOLIS, IN 46218  
ATTN BRANCH 942, D. J. REPASS

COMMANDER  
NAVAL ELECTRONIC SYSTEMS COMMAND  
HEADQUARTERS  
WASHINGTON, DC 20360  
ATTN PME 117-21  
ATTN ELEX 05323, CLEVELAND F. WATKINS  
ATTN CODE 504510  
ATTN CODE 5032, CHARLES W. NEILL  
ATTN CODE 504511, CHARLES R. SUMAN  
ATTN CODE 9053, TECH INFO SVCS BR

COMMANDING OFFICER  
NAVAL INTELLIGENCE SUPPORT CENTER  
4301 SUTLAND ROAD, BLDG 5  
WASHINGTON, DC 20390  
ATTN P. ALEXANDER  
ATTN NISC-45

DIRECTOR  
NAVAL RESEARCH LABORATORY  
WASHINGTON, DC 20375  
ATTN 6601, E. WOLICKI  
ATTN CODE 6631, JAMES C. RITTER  
ATTN CODE 4004, EMANUEL L. BRANCATO  
ATTN CODE 2627, DORIS R. FOLEN  
ATTN CODE 7701, JACK D. BROWN  
ATTN CODE 5216, HAROLD L. HUGHES  
ATTN CODE 5210, JOHN E. DAVEY

DISTRIBUTION (Cont'd)

NAVAL RESEARCH LAB (Cont'd)  
ATTN CODE 6440 GEORGE SIGEL  
ATTN CODE 2620, LIBRARY  
ATTN CODE 4000, RESEARCH DEPT  
ATTN CODE 6620, RADIATION EFFECTS

COMMANDER  
NAVAL SEA SYSTEMS COMMAND  
NAVY DEPARTMENT  
WASHINGTON, DC 20362  
ATTN SEA-9931, RILEY B. LANE  
ATTN SEA-9931, SAMUEL A. BARHAM  
ATTN SEA-09G32, TECH LIB

NAVAL SHIP ENGINEERING CENTER  
DEPT OF THE NAVY  
WASHINGTON, DC 20362  
ATTN CODE 6174D2, EDWARD F. DUFFY

COMMANDER  
NAVAL SURFACE WEAPONS CENTER  
WHITE OAK, SILVER SPRING, MD 20910  
ATTN CODE WX21, TECH LIB  
ATTN CODE WA501, NAVY NUC PRGMS OFF  
ATTN WA50  
ATTN CODE WA52, R. A. SMITH  
ATTN CODE WR, RESEARCH &  
TECHNOLOGY DEPT

COMMANDER  
NAVAL SURFACE WEAPONS CENTER  
DAHLGREN LABORATORY  
DAHLGREN, VA 22448  
ATTN WILLIAM H. HOLT  
ATTN DX-21, LIBRARY DIV

COMMANDER  
NAVAL WEAPONS CENTER  
CHINA LAKE, CA 93555  
ATTN CODE 533, TECHNICAL LIBRARY

COMMANDING OFFICER  
NAVAL WEAPONS EVALUATION FACILITY  
KIRTLAND AIR FORCE BASE  
ALBUQUERQUE, NM 87117  
ATTN CODE ATG, MR. STANLEY

COMMANDING OFFICER  
NAVAL WEAPONS SUPPORT CENTER  
CRANE, IN 47522  
ATTN CODE 7024, JAMES RAMSEY  
ATTN CODE 70242, JOSEPH A. MUNARIN

COMMANDING OFFICER  
NUCLEAR WEAPONS TRAINING CENTER PACIFIC  
NAVAL AIR STATION, NORTH ISLAND  
SAN DIEGO, CA 92135  
ATTN CODE 50

DIRECTOR  
STRATEGIC SYSTEMS PROJECT OFFICE  
NAVY DEPARTMENT  
WASHINGTON, DC 20376  
ATTN SP2701, JOHN W. PITSEMBERGER  
ATTN NSP-2342, RICHARD L. COLEMAN  
ATTN NSP-27331, PHIL SPECTOR

ASSISTANT SECRETARY OF THE AIR FORCE  
(RESEARCH & DEVELOPMENT)  
WASHINGTON, DC 20330

DEPUTY CHIEF OF STAFF, RES & DEV  
US AIR FORCE  
WASHINGTON, DC 20330  
ATTN RDQPN, S/V & NUCLEAR PROG DIV

COMMANDER  
AERONAUTICAL SYSTEMS DIC  
WRIGHT-PATTERSON AFB, OH 45433

COMMANDER-IN-CHIEF  
AEROSPACE DEFENSE COMMAND  
ENT AIR FORCE BASE, CO 80912  
ATTN TECHNICAL LIBRARY

COMMANDER  
AEROSPACE RESEARCH LABORATORIES  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN LS, SOLID STATE PHYSICS RES LAB

DIRECTOR  
AF AVIONICS LABORATORY  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN TE, ELECTRONIC TECHNOLOGY DIV  
ATTN TER, ELECTRONIC RES BR  
ATTN TSR, STINFO BR  
ATTN DHE, H. J. HENNECKE  
ATTN DHM, C. FRIEND  
ATTN DH, LTC MCKENZIE  
ATTN AAT, MASON FRIAR

COMMANDER  
AF CAMBRIDGE RESEARCH LABORATORIES,  
AFSC  
L. G. HANSCOM FIELD  
BEDFORD, MA 01730  
ATTN LQ, SOLID-STATE SCI LAB

COMMANDER  
AF FLIGHT DYNAMICS LAB  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN PTS, SURVIVABILITY/  
VULNERABILITY BR  
ATTN STS, TECH INFO BR

AF GEOPHYSICS LABORATORY, AFSC  
HANSCOM AFB, MA 01731  
ATTN J. EMERY CORMIER  
ATTN LGD-STOP 30, FREEMAN SHEPHERD  
ATTN LQR, EDWARD A. BURKE

AF INSTITUTE OF TECHNOLOGY, AU  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN ENP, CHARLES J. BRIDGMAN

AF MATERIALS LABORATORY, AFSC  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN LTE

AF WEAPONS LABORATORY, AFSC  
KIRTLAND AFB, NM 87117

ATTN ELA  
ATTN SAB  
ATTN ELP, TREE SECTION  
ATTN ELP, JULIAN NICHOLS  
ATTN DEX  
ATTN ELS  
ATTN NTS  
ATTN ELXT  
ATTN SE, NUCLEAR SYS DIV  
ATTN ELC, COMM & SATELLITE BR

AFTAC  
PATRICK AFB, FL 32925  
ATTN TFS, MAJ MARION F. SCHNEIDER  
ATTN TAE

COMMANDER  
ASD  
WPAFB, OH 45433  
ATTN ASD/ENESS, PETER T. MARTH  
ATTN ASD-YH-EX, LTC ROBERT LEVERETTE  
ATTN ENACC, ROBERT L. FISH

HEADQUARTERS  
ELECTRONIC SYSTEMS DIVISION, (AFSC)  
HANSCOM AFB, MA 01731  
ATTN YWEI  
ATTN YSEV

COMMANDER  
FOREIGN TECHNOLOGY DIVISION, AFSC  
WRIGHT-PATTERSON AFB, OH 45433  
ATTN ETET, CAPT RICHARD C. HUSEMANN

COMMANDER  
ROME AIR DEVELOPMENT CENTER, AFSC  
GRIFFISS AFB, NY 13440  
ATTN RBRAC, I. L. KRULAC  
ATTN RBRP, CLYDE LANE  
ATTN TUT, TEST & EVAL BR  
ATTN TUM, MATERIEL BR  
ATTN TIL, TECHNICAL LIBRARY

COMMANDER  
ROME AIR DEVELOPMENT CENTER, AFSC  
HANSCOM AFB, MA 01731  
ATTN ET, R. BUCHANAN  
ATTN ETS, R. DOLAN  
ATTN ETS, A KAHAN

DIRECTOR  
AF OFFICE OF SCIENTIFIC RESEARCH  
1400 WILSON BLVD  
ARLINGTON, VA 22209  
ATTN NE, DIR OF ELECTRONIC  
& SOLID STATE SCI

COMMANDER  
SPACE & MISSILE SYSTEMS ORGANIZATION  
(SAMSO)  
PO BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN RS, DEP FOR REENTRY SYS  
ATTN LV, DEP FOR LAUNCH VEHICLES  
ATTN SK, DEP FOR COMM SYS

COMMANDER  
AF SPECIAL WEAPONS CENTER (OAS)  
KIRTLAND AFB, NM 87117  
ATTN TE, TEST & EVAL SYS PROG OFC

COMMANDER  
HQ AIR FORCE SYSTEMS COMMAND  
ANDREWS AFB  
WASHINGTON, DC 20331  
ATTN TECHNICAL LIBRARY

SAMSO/DY  
POST OFFICE BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN DYS, MAJ LARRY A. DARDA  
ATTN DYS, CAPT WAYNE SCHOBEN  
ATTN DYS, CAPT E. MERZ

SAMSO/IN  
POST OFFICE BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN IND, I. J. JUDY

DISTRIBUTION (Cont'd)

SANSO/MN  
NORTON AFB, CA 92409  
ATTN MNNG, CAPT DAVID J. STROBEL  
ATTN MNMH

SANSO/RS  
POST OFFICE BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN RSSE, LTC KENNETH L. GILBERT  
ATTN RSMG, CAPT COLLIER

SANSO/SK  
POST OFFICE BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN SKF, PETER J. STADLER

SANSO/SZ  
POST OFFICE BOX 92960  
WORLDWAY POSTAL CENTER  
LOS ANGELES, CA 90009  
ATTN SZJ, CAPT JOHN H. SALCH

COMMANDER IN CHIEF  
STRATEGIC AIR COMMAND  
OFFUTT AFB, NE 68113  
ATTN NRI-STINFO LIBRARY  
ATTN XPFS, MAJ BRIAN STEPHAN

UNIVERSITY OF CALIFORNIA  
LAWRENCE LIVERMORE LABORATORY  
PO BOX 808  
LIVERMORE, CA 94550  
ATTN DONALD J. MEEKER, L-545  
ATTN JOSEPH E. KELLER, JR., L-125  
ATTN RONALD L. OTT, L-531  
ATTN HANS KRUGER, L-96  
ATTN LAWRENCE CLELAND, L-156  
ATTN FREDERICK R. KOVAR, L-31  
ATTN TECH INFO DEPT, L-3

LOS ALAMOS SCIENTIFIC LABORATORY  
P.O. BOX 1663  
LOS ALAMOS, NM 87544  
ATTN MARVIN M. HOFFMAN  
ATTN J. ARTHUR FREED  
ATTN BRUCE W. NOEL

SANDIA LABORATORIES  
LIVERMORE LABORATORY  
PO BOX 969  
LIVERMORE, CA 94550  
ATTN THEODORE A. DELLIN

SANDIA LABORATORIES  
PO BOX 5800  
ALBUQUERQUE, NM 87115  
ATTN 3141 SANDIA RPT COLL  
ATTN ORG 2110, J. A. HOOD  
ATTN JACK V. WALKER, 5220  
ATTN ORG 1933, F. N. COPPAGE  
ATTN DIV 5231, JAMES H. RENKEN  
ATTN R. GREGORY, ORG 2140

ADMINISTRATOR  
NASA HEADQUARTERS  
WASHINGTON, DC 20546  
ATTN OFC OF AERONAUTICS  
AND SPACE TECHNOLOGY

AMES RESEARCH CENTER  
NASA  
MOFFETT FIELD, CA 94035  
ATTN DIR OF RESEARCH SUPPORT

DIRECTOR  
NASA  
GODDARD SPACE FLIGHT CENTER  
GREENBELT, MD 20771  
ATTN 250, TECH INFO DIV

DIRECTOR  
NSAS  
HUGH L. DRYDEN FLIGHT RESEARCH CENTER  
EDWARDS, CA 93523  
ATTN TECHNICAL LIBRARY

DIRECTOR  
NASA  
JOHN F. KENNEDY SPACE CENTER, FL 32899  
ATTN TECHNICAL LIBRARY

DIRECTOR  
NASA  
LEWIS RESEARCH CENTER  
CLEVELAND, OH 44135  
ATTN TECHNICAL LIBRARY

JET PROPULSION LABORATORY  
CALIFORNIA INSTITUTE OF TECHNOLOGY  
4800 OAK GROVE DRIVE  
PASADENA, CA 91103  
ATTN TECHNICAL LIBRARY

DIRECTOR  
NASA  
LANGLEY RESEARCH CENTER  
HAMPTON, VA 23665  
ATTN TECHNICAL LIBRARY  
ATTN INSTR RES DIV

DIRECTOR  
NASA  
GEORGE C. MARSHALL SPACE FLIGHT CENTER  
MARSHALL SPACE FLIGHT CENTER, AL 35812  
ATTN EA, SCI & ENGR  
ATTN EC, ELECTRONICS & CONTROL LAB  
ATTN EC-21, GUIDANCE, CONTROL  
& INSTR DIV  
ATTN EC-41, ELECTRONICS DEV DIV  
ATTN ES-21, RADIATION & LOW TEMP SCI  
ATTN ES-31, PHYSICS & INSTR DIV

CENTRAL INTELLIGENCE AGENCY  
ATTN: RD/SI, RM 5G4B, HQ BLDG  
WASHINGTON, DC 20505  
ATTN ALICE A. PADGETT

DEPARTMENT OF COMMERCE  
NATIONAL BUREAU OF STANDARDS  
WASHINGTON, DC 20234  
ATTN APPL RAD DIV, ROBERT C. PLACIOUS  
ATTN JUDSON C. FRENCH

AEROJET ELECTRO-SYSTEMS CO. DIV.  
AEROJET-GENERAL CORPORATION  
P.O. BOX 296  
AZUSA, CA 91702  
ATTN THOMAS D. HANSCOME, B170/D6711

AEROSPACE CORPORATION  
PO BOX 92957  
LOS ANGELES, CA 90009  
ATTN IRVING M. GARFUNKEL  
ATTN JULIAN REINHEIMER  
ATTN LIBRARY  
ATTN MELVIN J. BERNSTEIN  
ATTN WILLIAM W. WILLIS  
ATTN S. P. BOWER  
ATTN JOHN DITRE  
ATTN L. W. AUKERMAN

ANALOG TECHNOLOGY CORPORATION  
3410 EAST FOOTHILL BOULEVARD  
PASADENA, CA 91107  
ATTN JOHN JOSEPH BAUM

AVCO RESEARCH & SYSTEMS GROUP  
201 LOWELL STREET  
WILMINGTON, MA 01887  
ATTN RESEARCH LIB, A830, RM 7201

BDM CORPORATION, THE  
1920 ALINE AVE  
VIENNA, VA 22180  
ATTN T. H. NEIGHBORS

BDM CORPORATION, THE  
PO BOX 9274  
ALBUQUERQUE INTERNATIONAL  
ALBUQUERQUE, NM 87119  
ATTN D. R. ALEXANDER

BENDIX CORPORATION, THE  
COMMUNICATION DIVISION  
EAST JOPPA ROAD - TOWSON  
BALTIMORE, MD 21204  
ATTN DOCUMENT CONTROL

BENDIX CORPORATION, THE  
RESEARCH LABORATORIES DIV  
BENDIX CENTER  
SOUTHFIELD, MI 48075  
ATTN MGR PRGM DEV, DONALD J. NIEHAUS  
ATTN MAX FRANK

BOEING COMPANY, THE  
PO BOX 3707  
SEATTLE, WA 98124  
ATTN HOWARD W. WICKLEIN, MS 17-11  
ATTN DAVID DYE, MS 87-75  
ATTN AEROSPACE LIBRARY  
ATTN ROBERT S. CALDWELL, 2R-00

BOOZ-ALLEN AND HAMILTON, INC.  
106 APPLE STREET  
NEW SHREWSBURY, NJ 07724  
ATTN R. J. CHRISNER

CALIFORNIA INSTITUTE OF TECHNOLOGY  
JET PRCPULSION LABORATORY  
4800 OAK PARK GROVE  
PASADENA, CA 91103  
ATTN J. BRYDEN  
ATTN A. G. STANLEY

CHARLES STARK DRAPER LABORATORY INC.  
68 ALBANY STREET  
CAMBRIDGE, MA 02139  
ATTN KENNETH FERTIG  
ATTN PAUL R. KELLY  
ATTN RICHARD G. HALTMAIER

CINCINNATI ELECTRONICS CORPORATION  
2630 GLENDALE - MILFORD ROAD  
CINCINNATI, OH 45241  
ATTN C. R. STUMP  
ATTN LOIS HAMMOND

COMPUTER SCIENCES CORPORATION  
201 LA VETA DRIVE, NE  
ALBUQUERQUE, NM 87108  
ATTN RICHARD H. DICKHAUT

DISTRIBUTION (Cont'd)

CUTLER-HAMMER, INC.  
AII DIVISION  
COMAC ROAD  
DEER PARK, NY 11729  
ATTN CENTRAL TECH FILES, ANN ANTHONY

DIKEWOOD CORPORATION, THE  
1009 BRADBURY DRIVE, SE  
UNIVERSITY RESEARCH PARK  
ALBUQUERQUE, NM 87106  
ATTN L. WAYNE DAVIS

E-SYSTEMS, INC.  
GREENVILLE DIVISION  
PO BOX 1056  
GREENVILLE, TX 75401  
ATTN LIBRARY 8-50100

EFFECTS TECHNOLOGY, INC.  
5383 HOLLISTER AVENUE  
SANTA BARBARA, CA 93105  
ATTN EDWARD JOHN STEELE

EXPERIMENTAL AND MATHEMATICAL  
PHYSICS CONSULTANTS  
P. O. BOX 66331  
LOS ANGELES, CA 90066  
ATTN THOMAS M. JORDAN

FAIRCHILD CAMERA AND INSTRUMENT  
CORPORATION  
464 ELLIS STREET  
MOUNTAIN VIEW, CA 94040  
ATTN 2-233, MR. DAVID K. MYERS

FAIRCHILD INDUSTRIES, INC.  
SHERMAN FAIRCHILD TECHNOLOGY CENTER  
20301 CENTURY BOULEVARD  
GERMANTOWN, MD 20767  
ATTN MGR CONFIG DATA & STANDARDS

FLORIDA, UNIVERSITY OF  
AN INSTITUTION OF EDUCATION  
ATTN: PATRICIA B. RAMBO  
P.O. BOX 284  
GAINESVILLE, FL 32601  
ATTN D. P. KENNEDY

FORD AEROSPACE & COMMUNICATIONS CORP  
3939 FABIAN WAY  
PALO ALTO, CA 94303  
ATTN SAMUEL R. CRAWFORD, MS 531  
ATTN EDWARD R. HAHN, MS-X22  
ATTN DONALD R. MCMORROW, MS G30

FORD AEROSPACE & COMMUNICATIONS  
OPERATIONS  
FORD & JAMBOREE ROADS  
NEWPORT BEACH, CA 92663  
ATTN KEN C. ATTINGER  
ATTN E. R. PONCELET, JR  
ATTN TECH INFO SECTION

FRANKLIN INSTITUTE, THE  
20TH STREET AND PARKWAY  
PHILADELPHIA, PA 19103  
ATTN RAMIE H. THOMPSON

GARRETT CORPORATION  
P.O. BOX 92248  
LOS ANGELES, CA 90009  
ATTN ROBERT E. WEIR, DEPT. 93-9

GENERAL DYNAMICS CORP  
ELECTRONICS DIV ORLANDO OPERATIONS  
PO BOX 2566  
ORLANDO, FL 32802  
ATTN D. W. COLEMAN

GENERAL ELECTRIC COMPANY  
SPACE DIVISION  
VALLEY FORGE SPACE CENTER  
GODDARD BLVD KING OF PRUSSIA  
P.O. BOX 8555  
PHILADELPHIA, PA 19101  
ATTN LARRY I. CHASEN  
ATTN JOSEPH C. PEDEN, CCF 8301  
ATTN JOHN L. ANDREWS

GENERAL ELECTRIC COMPANY  
RE-ENTRY & ENVIRONMENTAL SYSTEMS DIV  
PO BOX 7722  
3198 CHESTNUT STREET  
PHILADELPHIA, PA 19101  
ATTN JOHN W. PALCHEFSKY, JR.  
ATTN ROBERT V. BENEDICT  
ATTN RAY E. ANDERSON

GENERAL ELECTRIC COMPANY  
ORDNANCE SYSTEMS  
100 PLASTICS AVENUE  
PITTSFIELD, MA 01201  
ATTN JOSEPH J. REIDL

GENERAL ELECTRIC COMPANY  
TEMPO-CENTER FOR ADVANCED STUDIES  
816 STATE STREET (PO DRAWER QQ)  
SANTA BARBARA, CA 93102  
ATTN DASIAC  
ATTN ROYDEN R. RUTHERFORD  
ATTN M ESPIG

GENERAL ELECTRIC COMPANY  
PO BOX 1122  
SYRACUSE, NY 13201  
ATTN CSP 0-7, L. H. DEE

GENERAL ELECTRIC COMPANY  
AIRCRAFT ENGINE GROUP  
EVENDALE PLANT  
CINCINNATI, OH 45215  
ATTN JOHN A. ELLERHORST, E2

GENERAL ELECTRIC COMPANY  
AEROSPACE ELECTRONICS SYSTEMS  
FRENCH ROAD  
UTICA, NY 13503  
ATTN CHARLES M. HEWISON, DROP 624  
ATTN W. J. PATTERSON, DROP 233

GENERAL ELECTRIC COMPANY  
PO BOX 5000  
BINGHAMTON, NY 13902  
ATTN DIVID W. PEPIN, DROP 160

GENERAL ELECTRIC COMPANY-TEMPO  
ATTN: DASIAC  
C/O DEFENSE NUCLEAR AGENCY  
WASHINGTON, DC 20305  
ATTN WILLIAM ALFONTE

GENERAL RESEARCH CORPORATION  
P.O. BOX 3587  
SANTA BARBARA, CA 93105  
ATTN ROBERT D. HILL

GEORGIA INSTITUTE OF TECHNOLOGY  
GEORGIA TECH RESEARCH INSTITUTE  
ATLANTA, GA 30332  
ATTN R. CURRY

GRUMMAN AEROSPACE CORPORATION  
SOUTH OYSTER BAY ROAD  
BETHPAGE, NY 11714  
ATTN JERRY ROGERS, DEPT 533

GTE SYLVANIA, INC.  
ELECTRONICS SYSTEMS GRP-EASTERN DIV  
77 A STREET  
NEEDHAM, MA 02194  
ATTN CHARLES A. THORNHILL, LIBRARIAN  
ATTN LEONARD L. BLAISDELL  
ATTN JAMES A. WALDON

GTE SYLVANIA, INC.  
189 B STREET  
NEEDHAM HEIGHTS, MA 02194  
ATTN CHARLES H. RAMSBOTTOM  
ATTN HERBERT A. ULLMAN  
ATTN H & V GROUP  
ATTN PAUL B. FREDRICKSON

GULTON INDUSTRIES, INC.  
ENGINEERED MAGNETICS DIVISION  
13041 CERISE AVENUE  
HAWTHORNE, CA 90250  
ATTN ENGMAGNETICS DIV

HARRIS CORPORATION  
HARRIS SEMICONDUCTOR DIVISION  
P.O. BOX 883  
MELBOURNE, FL 32901  
ATTN C. F. DAVIS, MS 17-220  
ATTN T. CLARK, MS 4040  
ATTN WAYNE E. ABARE, MS 16-111

HAZELTINE CORPORATION  
PULASKI ROAD  
GREEN LAWN, NY 11740  
ATTN TECH INFO CTR, M. WAITE

HONEYWELL INCORPORATED  
GOVERNMENT AND AERONAUTICAL  
PRODUCTS DIVISION  
2600 RIDGEWAY PARKWAY  
MINNEAPOLIS, MN 55413  
ATTN RONALD R. JOHNSON, A1622  
ATTN R. J. KELL, MS S2572

HONEYWELL INCORPORATED  
AEROSPACE DIVISION  
13350 US HIGHWAY 19  
ST. PETERSBURG, FL 33733  
ATTN HARRISON H. NOBLE, MS 725-5A  
ATTN MS 725-J, STACEY H. GRAFF

HONEYWELL INCORPORATED  
RADIATION CENTER  
2 FORBES ROAD  
LEXINGTON, MA 02173  
ATTN TECHNICAL LIBRARY

HUGHES AIRCRAFT COMPANY  
CENTINELLA & TEALE  
CULVER CITY, CA 90230  
ATTN M.S. D157, KEN WALKER  
ATTN B. W. CAMPBELL, M.S. 6-E110  
ATTN DAN BINDER, MS 6-D147  
ATTN JOHN B. SINGLETARY, MS 6-D133

DISTRIBUTION (Cont'd)

HUGHES AIRCRAFT COMPANY  
SPACE SYSTEMS DIVISION  
P.O. BOX 92919  
LOS ANGELES, CA 90009  
ATTN WILLIAM W. SCOTT, MS A1080  
ATTN EDWARD C. SMITH, MS A620

IBM CORPORATION  
ROUTE 17C  
OWEGO, NY 13827  
ATTN HARRY W. MATHERS, DEPT M41  
ATTN FRANK FRANKOVSKY

INTL TEL & TELEGRAPH CORPORATION  
500 WASHINGTON AVENUE  
NUTLEY, NJ 07110  
ATTN ALEXANDER T. RICHARDSON

ION PHYSICS CORPORATION  
SOUTH BEDFORD STREET  
BURLINGTON, MA 01803  
ATTN ROBERT D. EVANS

IRT CORPORATION  
P.O. BOX 81087  
SAN DIEGO, CA 92138  
ATTN LEO D. COTTER  
ATTN RALPH H. STAHL  
ATTN JAMES A. NABER  
ATTN R. L. MERTZ  
ATTN MDC

JAYCOR  
205 S. WHITING STREET, SUITE 500  
ALEXANDRIA, VA 22304  
ATTN ROBERT SULLIVAN  
ATTN CATHERINE TUESKO

JOHNS HOPKINS UNIVERSITY  
APPLIED PHYSICS LABORATORY  
JOHNS HOPKINS ROAD  
LAUREL, MD 20810  
ATTN PETER E. PARTRIDGE

KAMAN SCIENCES CORPORATION  
P.O. BOX 7463  
COLORADO SPRINGS, CO 80933  
ATTN DONALD H. BRYCE  
ATTN ALBERT P. BRIDGES  
ATTN WALTER E. WARE  
ATTN JOHN R. HOFFMAN  
ATTN JERRY I. LUBELL

LITTON SYSTEMS, INC.  
GUIDANCE & CONTROL SYSTEMS DIVISION  
5500 CANOGA AVENUE  
WOODLAND HILLS, CA 91364  
ATTN VAL J. ASHBY, MS 67  
ATTN JOHN P. RETZLER

LITTON SYSTEMS, INC.  
ELECTRON TUBE DIVISION  
1035 WESTMINSTER DRIVE  
WILLIAMSPORT, PA 17701  
ATTN FRANK J. MCCARTHY

LOCKHEED MISSILES AND SPACE  
COMPANY, INC.  
P.O. BOX 504  
SUNNYVALE, CA 94088  
ATTN G. F. HEATH, D/81-14  
ATTN PHILIP J. HART, DEPT 81-14  
ATTN BENJAMIN T. KIMURA, DEPT 81-14  
ATTN EDWIN A. SMITH, DEPT 85-85  
ATTN L. ROSSI, DEPT 81-64

LOCKHEED MISSILES AND SPACE (Cont'd)  
ATTN G. H. MORRIS, 81-01  
ATTN DEPT 85-85, SAMUEL I. TAIMUTY

LOCKHEED MISSILES AND SPACE COMPANY  
3251 HANOVER STREET  
PALO ALTO, CA 94304  
ATTN TECH INFO CTR D/COLL

LTV AEROSPACE CORPORATION  
VOUGHT SYSTEMS DIVISION  
P.O. BOX 6267  
DALLAS, TX 75222  
ATTN TECHNICAL DATA CENTER

LTV AEROSPACE CORPORATION  
PO BOX 5907  
DALLAS, TX 75222  
ATTN TECHNICAL DATA CTR

M.I.T. LINCOLN LABORATORY  
P.O. BOX 73  
LEXINGTON, MA 02173  
ATTN LEONA LOUGHLIN, LIBRARIAN, A-082

MARTIN MARIETTA AEROSPACE  
ORLANDO DIVISION  
P.O. BOX 5837  
ORLANDO, FL 32805  
ATTN MONA C. GRIFFITH, LIB MP-30  
ATTN WILLIAM W. MRAS, MP-413  
ATTN JACK M. ASHFORD, MP-537

MARTIN MARIETTA CORPORATION  
DENVER DIVISION  
PO BOX 179  
DENVER, CO 80201  
ATTN J. E. GOODWIN, MAIL 0452  
ATTN RESEARCH LIB, 6617, J. R. MCKEE  
ATTN PAUL G. KASE, MAIL 8203  
ATTN BEN T. GRAHAM, MS PO-454

MCDONNELL DOUGLAS CORPORATION  
POST OFFICE BOX 516  
ST. LOUIS, MO 63166  
ATTN TOM ENDER  
ATTN TECHNICAL LIBRARY

MCDONNELL DOUGLAS CORPORATION  
5301 BOLSA AVENUE  
HUNTINGTON BEACH, CA 92647  
ATTN STANLEY SCHNEIDER

MCDONNELL DOUGLAS CORPORATION  
3855 LAKEWOOD BOULEVARD  
LONG BEACH, CA 90846  
ATTN TECHNICAL LIBRARY, C1-290/36-84

MISSION RESEARCH CORPORATION  
735 STATE STREET  
SANTA BARBARA, CA 93101  
ATTN WILLIAM C. HART

MISSION RESEARCH CORPORATION-SAN DIEGO  
7650 CONVOY COURT  
SAN DIEGO, CA 92111  
ATTN V. A. J. VAN LINT  
ATTN J. P. RAYMOND

MITRE CORPORATION, THE  
P.O. BOX 208  
BEDFORD, MA 01730  
ATTN LIBRARY  
ATTN M. F. FITZGERALD

NATIONAL ACADEMY OF SCIENCES  
2101 CONSTITUTION AVE,  
WASHINGTON, DC 20418  
ATTN DR. R. S. SHANE,  
NAT MATERIALS ADVISORY BO

NEW MEXICO, UNIVERSITY OF  
DEPT OF CAMPUS SECURITY AND POLICE  
1821 ROMA NE  
ALBUQUERQUE, NM 87106  
ATTN W. W. GRANNEMANN

NEW MEXICO, UNIVERSITY OF  
ELECTRICAL ENGINEERING  
& COMPUTER SCIENCE DEPT  
ALBUQUERQUE, NM 87131  
ATTN HAROLD SOUTHWARD

NORTHROP CORPORATION  
ELECTRONIC DIVISION  
1 RESEARCH PARK  
PALOS VERDES PENINSULA, CA 90274  
ATTN JOHN M. REYNOLDS  
ATTN VINCENT R. DEMARTINO  
ATTN BOYCE T. AHLPORT  
ATTN GEORGE H. TOWNER

NORTHROP CORPORATION  
NORTHROP RESEARCH AND TECHNOLOGY CENTER  
3401 WEST BROADWAY  
HAWTHORNE, CA 90250  
ATTN DAVID N. POCOCK  
ATTN J. R. SROUR  
ATTN ORLIE L. CURTIS

NORTHROP CORPORATION  
ELECTRONIC DIVISION  
2301 WEST 120TH STREET  
HAWTHORNE, CA 90250  
ATTN JOSEPH D. RUSSO

PALISADES INST FOR RSCH SERVICES INC.  
201 VARICK STREET  
NEW YORK, NY 10014  
ATTN RECORDS SUPERVISOR

PHYSICS INTERNATIONAL COMPANY  
2700 MERCED STREET  
SAN LEANDRO, CA 94577  
ATTN CHARLES H. STALLINGS  
ATTN JOHN H. HUNTINGTON

POWER PHYSICS CORPORATION  
542 INDUSTRIAL WAY WEST  
PO BOX 626  
EATONTOWN, NJ 07724  
ATTN MITCHELL BAKER

R & D ASSOCIATES  
PO BOX 9695  
MARINA DEL REY, CA 90291  
ATTN S. CLAY ROGERS

RAYTHEON COMPANY  
HARTWELL ROAD  
BEDFORD, MA 01730  
ATTN GAJANAN H. JOSHI, RADAR SYS LAB

RATHEON COMPANY  
528 BOSTON POST ROAD  
SUDBURY, MA 01776  
ATTN HAROLD L. FLESCHER

# DISTRIBUTION (Cont'd)

RCA CORPORATION  
GOVERNMENT & COMMERCIAL SYSTEMS  
ASTRO ELECTRONICS DIVISION  
PO BOX 800, LOCUST CORNER  
PRINCETON, NJ 08540  
ATTN GEORGE J. BRUCKER

RCA CORPORATION  
DAVID SARNOFF RESEARCH CENTER  
W. WINDSOR TWP  
201 WASHINGTON ROAD, PO BOX 432  
PRINCETON, NJ 08540  
ATTN K. H. ZAININGER

RCA CORPORATION  
CAMDEN COMPLEX  
FRONT & COOPER STREETS  
CAMDEN, NJ 08012  
ATTN E. VAN KEUREN, 13-5-2

RENSSELAER POLYTECHNIC INSTITUTE  
PO BOX 965  
TROY, NY 12181  
ATTN RONALD J. GUTMANN

RESEARCH TRIANGLE INSTITUTE  
PO BOX 12194  
RESEARCH TRIANGLE PARK, NC 27709  
ATTN SEC OFFICER FOR  
ENG DIV, MAYRANT SIMONS, JR.

ROCKWELL INTERNATIONAL CORPORATION  
3370 MIROLOMA AVENUE  
ANAHEIM, CA 92803  
ATTN K. F. HULL  
ATTN JAMES E. BELL, HA10  
ATTN DONALD J. STEVENS, FA70  
ATTN GEORGE C. MESSENGER, FB61  
ATTN N. J. RUDIE, FA53

ROCKWELL INTERNATIONAL CORPORATION  
5701 WEST IMPERIAL HIGHWAY  
LOS ANGELES, CA 90009  
ATTN T. B. YATES

ROCKWELL INTERNATIONAL CORPORATION  
ELECTRONICS OPERATIONS  
COLLINS RADIO GROUP  
5225 C. AVENUE NE  
CEDAR RAPIDS, IA 52406  
ATTN ALAN A. LANGENFELD  
ATTN DENNIS SUTHERLAND  
ATTN MILDRED A. BLAIR

SANDERS ASSOCIATES, INC.  
95 CANAL STREET  
NASHUA, NH 03060  
ATTN M. L. AITEL, NCA 1-3236

SCIENCE APPLICATIONS, INC.  
PO BOX 2351  
LA JOLLA, CA 92038  
ATTN LARRY SCOTT  
ATTN J. ROBERT BEYSTER

SCIENCE APPLICATIONS, INC.  
HUNTSVILLE DIVISION  
2109 W. CLINTON AVENUE  
SUITE 700  
HUNTSVILLE, AL 35805  
ATTN NOEL R. BYRN

SCIENCE APPLICATIONS, INC.  
2680 HANOVER STREET  
PALO ALTO, CA 94303  
ATTN CHARLES STEVENS

SCIENCE APPLICATIONS, INC.  
8400 WESTPARK DRIVE  
MCLEAN, VA 22101  
ATTN WILLIAM L. CHADSEY  
SIMULATION PHYSICS, INC.  
41 "B" STREET  
BURLINGTON, MA 01803  
ATTN ROGER G. LITTLE

SINGER COMPANY, THE  
1150 MC BRIDE AVENUE  
LITTLE FALLS, NJ 07424  
ATTN IRWIN GOLDMAN, ENG MANAGEMENT

SINGER COMPANY (DATA SYSTEMS), THE  
150 TOTOWA ROAD  
WAYNE, NJ 07470  
ATTN TECH INFO CENTER

SPERRY FLIGHT SYSTEMS DIVISION  
SPERRY RAND CORPORATION  
P.O. BOX 21111  
PHOENIX, AZ 85036  
ATTN D. ANDREW SCHOW

SPERRY RAND CORPORATION  
UNIVAC DIVISION  
DEFENSE SYSTEMS DIVISION  
P.O. BOX 3525 MAIL STATION 1931  
ST. PAUL, MN 55101  
ATTN JAMES A. INDA, MS 41T25

SPERRY RAND CORPORATION  
SPERRY DIVISION  
SPERRY GYROSCOPE DIVISION  
SPERRY SYSTEMS MANAGEMENT DIVISION  
MARCUS AVENUE  
GREAT NECK, NY 11020  
ATTN PAUL MARRAFFINO  
ATTN CHARLES L. CRAIG EV

STANFORD RESEARCH INSTITUTE  
333 RAVENSWOOD AVENUE  
MENLO PARK, CA 94025  
ATTN MR. PHILIP DOLAN

STANFORD RESEARCH INSTITUTE  
306 WYNN DRIVE, N. W.  
HUNTSVILLE, AL 35805  
ATTN MACPHERSON MORGAN

SUNDSTRAND CORPORATION  
4751 HARRISON AVENUE  
ROCKFORD, IL 61101  
ATTN DEPT 763SW, CURTIS WHITE

SYSTRON-DONNER CORPORATION  
1090 SAN MIGUEL ROAD  
CONCORD, CA 94518  
ATTN HAROLD D. MORRIS  
ATTN GORDON B. DEAN

TEXAS INSTRUMENTS, INC.  
P.O. BOX 5474  
DALLAS, TX 75222  
ATTN DONALD J. MANUS, MS 72

TEXAS TECH UNIVERSITY  
PO BOX 5404 NORTH COLLEGE STATION  
LUBBOCK, TX 79417  
ATTN TRAVIS L. SIMPSON

TRW SYSTEMS GROUP  
ONE SPACE PARK  
REDONDO BEACH, CA 90278  
ATTN TECH INFO CENTER/S-1930  
ATTN O. E. ADAMS, R1-1144  
ATTN R. K. FLEBUCH, R1-2078  
ATTN ROBERT M. WEBB, R1-2410  
ATTN H. H. HOLLOWAY, R1-2036

TRW SYSTEMS GROUP  
SAN BERNARDINO OPERATIONS  
PO BOX 1310  
SAN BERNARDINO, CA 92402  
ATTN EARL W. ALLEN  
ATTN F. B. FAY, 527/710  
ATTN R. KITTER

UNITED TECHNOLOGIES CORPORATION  
HAMILTON STANDARD DIVISION  
BRADLEY INTERNATIONAL AIRPORT  
WINDSOR LOCKS, CT 06069  
ATTN RAYMOND G. GIGUERE

WESTINGHOUSE ELECTRIC CORPORATION  
DEFENSE AND ELECTRONIC SYSTEMS CENTER  
P.O. BOX 1693  
FRIENDSHIP INTERNATIONAL AIRPORT  
BALTIMORE, MD 21203  
ATTN HENRY P. KALAPACA, MS 3525

HARRY DIAMOND LABORATORIES  
ATTN MCGREGOR, THOMAS, COL, COMMANDING  
OFFICER/FLYER, I.N./LANDIS, P.E./  
SOMMER, H./OSWALD, R. B.  
ATTN CARTER, W.W., DR., ACTING TECHNICAL  
DIRECTOR/MARCUS, S.M.  
ATTN KIMMEL, S., IO  
ATTN CHIEF, 0021  
ATTN CHIEF, 0022  
ATTN CHIEF, LAB 100  
ATTN CHIEF, LAB 200  
ATTN CHIEF, LAB 300  
ATTN CHIEF, LAB 400  
ATTN CHIEF, LAB 500  
ATTN CHIEF, LAB 600  
ATTN CHIEF, DIV 700  
ATTN CHIEF, DIV 800  
ATTN CHIEF, LAB 900  
ATTN CHIEF, LAB 1000  
ATTN RECORD COPY, BR 041  
ATTN HDL LIBRARY (3 COPIES)  
ATTN CHAIRMAN, EDITORIAL COMMITTEE  
ATTN CHIEF, 047  
ATTN TECH REPORTS, 013  
ATTN PATENT LAW BRANCH, 071  
ATTN MCLAUGHLIN, P.W., 741  
ATTN LANHAM, C., PROGRAM & PLANS OFFICE  
ATTN TOMPKINS, J. E., 230  
ATTN MILETTA, J. R., 240  
ATTN ROSADO, JOHN A., 240  
ATTN CALDWELL, PAUL A., 290  
ATTN WIMENITZ, F. N., 0024  
ATTN SOKOLOSKI, M. S., 0024  
ATTN MCGARRITY, J. M., 280  
ATTN HALPIN, J. J., 280  
ATTN BOESCH, H. E., JR. (15 COPIES)  
ATTN MCLEAN, F. B., 280  
ATTN WINOKUR, P. S., 280