


AD-A039 639

GEORGE WASHINGTON UNIV WASHINGTON D C SCHOOL OF ENGI--ETC F/G 11/6  
DETERMINATION OF CYCLIC NONLINEAR ENERGY TOUGHNESS FOR 7075-T6 --ETC(U)  
DEC 76 P K POULOSE, D L JONES, H LIEBOWITZ N00019-76-C-0151

UNCLASSIFIED


NL

1 OF 1  
AD  
A039639



END

DATE  
FILMED  
6-77

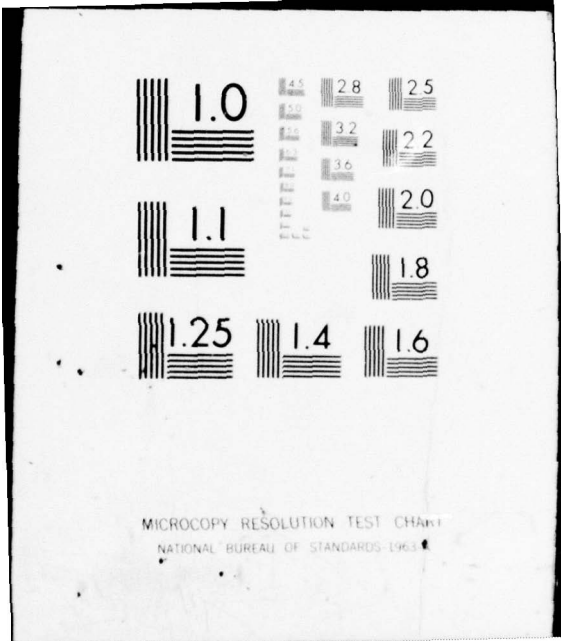


MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

ADA 039639

(72) J

THE  
GEORGE  
WASHINGTON  
UNIVERSITY

STUDENTS FACULTY STUDY R  
ESEARCH DEVELOPMENT FUT  
URE CAREER CREATIVITY CO  
MMUNITY LEADERSHIP TECH  
NOLOGY FRONTIER DESIGN  
ENGINEERING APPREHENSIVE  
GEORGE WASHINGTON UNIV

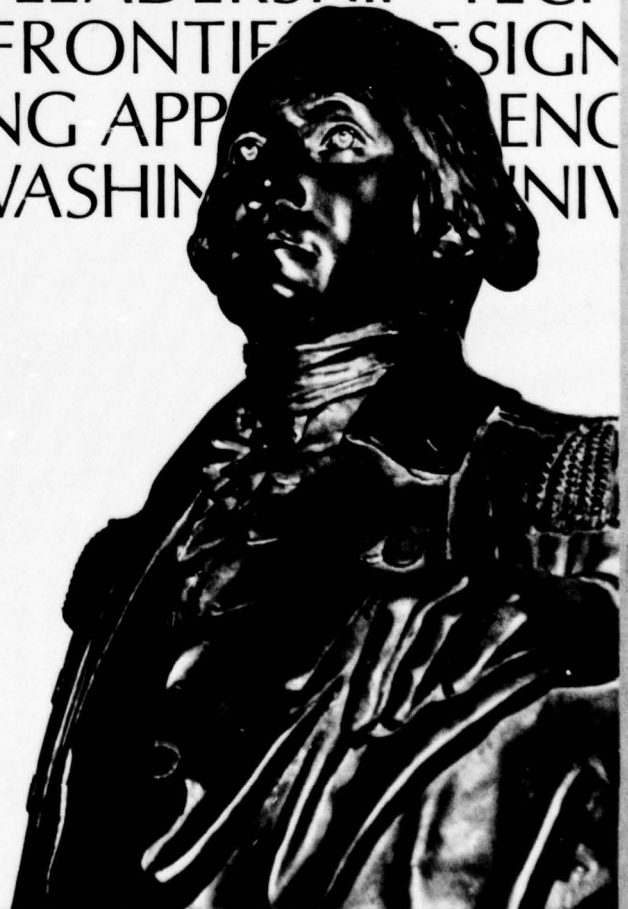

AD No. \_\_\_\_\_  
DDC FILE COPY

DDC  
MAY 19 1977  
B

SCHOOL OF ENGINEERING  
AND APPLIED SCIENCE

DETERMINATION OF CYCLIC  
NONLINEAR ENERGY TOUGHNESS  
FOR 7075-T6 ALUMINUM SHEETS

P. K. Poulouse, D. L. Jones, and H. Liebowitz

Final Scientific Report

Contract Number  
N00019-76-C-0151

December 1976

School of Engineering and Applied Science  
The George Washington University  
Washington, D. C. 20052

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DDI	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION.....	
BY.....	
DISTRIBUTION/AVAILABILITY CODES	
Doc.	AVAIL. and/or SPECIAL
A	

## ABSTRACT

In this report, the nonlinear energy method for fracture toughness determination has been applied to cyclic loading conditions. The nonlinear energy toughness for cyclic loading,  $\tilde{G}_{fc}$ , was obtained from an envelope of the cyclic load-displacement record for thin center-cracked sheet specimens of 7075-T6 aluminum alloy. A cyclic loading program, in which each succeeding load peak approached the static load in an exponential manner, was applied to these specimens. With constant specimen dimensions, different load increments were used for different specimens, which resulted in varying cyclic lives.

The specimens used in these tests exhibited a significant reduction in  $\tilde{G}_{fc}$  with increasing cyclic life in a manner analogous to the classical S-N diagram. This reduction in life for 7075-T6 was significantly less than for 2024-T3, which had been evaluated previously, although 2024-T3 has considerably higher toughness.

## INTRODUCTION

Plane strain fracture toughness testing of the new high-strength, high-toughness alloys often requires specimens of very large thicknesses that are difficult and expensive to test. Further, members of such large thickness are not usually employed in structures and, hence, the test results with thick specimens yield a highly conservative estimate of load carrying capacities of structural components. Because of the inadequacy of the linear fracture toughness test method, several nonlinear methods such as the R curve [1] the J integral [2-4] and the COD [5,6] methods have been suggested. However, these methods do not provide an exact treatment of crack-tip plasticity and are unable to properly incorporate subcritical crack growth into their respective toughness parameters.

The nonlinear energy method, developed at The George Washington University [7,8], is based on a global energy balance criterion applicable to both brittle and semibrittle fracture, and also to situations involving subcritical crack growth. From this consideration a toughness criterion was defined and an expression for nonlinear energy toughness,  $\tilde{G}_c$  was developed. This criterion has been examined for several materials and specimen geometries [9-11], and comparisons have been made with other nonlinear toughness parameters. The nonlinear energy toughness  $\tilde{G}_c$  or  $\tilde{G}_{Ic}$  has been found to give satisfactory results in all of these cases.

The classical approach to studying the behavior of un-notched materials under cyclic loading conditions has been to determine experimentally the cyclic life corresponding to a given load amplitude. Then, a plot of the material strength as a function of the cyclic life provides the conventional S-N diagram for that material. For specimens or components containing sharp cracks or notches subjected to cyclic loading, a fracture toughness approach, rather than the S-N curve, represents a better characterization of the remaining life. Although some attention has been given to applying the  $J$  integral to fatigue crack initiation [12], only theoretical considerations have been made. Therefore, the matter of the practical determination of fracture toughness values under cyclic loading has not been adequately addressed.

The nonlinear energy method has been examined for its applicability to certain sequences of cyclic loading of cracked specimens and an experimental procedure has been employed that incorporates the cyclic effects into the fracture toughness [13]. Thin sheet specimens of 2024-T3 aluminum alloy were tested at loads increasing as an exponential function of the cycle number. The limited number of data obtained exhibited an approximately linear decrease in toughness when plotted against the logarithm of the number of cycles to failure, and thus resembled in appearance a compressed S-N curve.

In this report, an attempt has been made to determine the behavior of the more brittle 7075-T6 alloy under cyclic

loading and to evaluate the cyclic nonlinear energy toughness,  $\tilde{G}_{fc}$ , as a function of the cyclic life. A larger range of the exponential increment than that used for 2024-T3 alloy has been employed in this program.

### THE $\tilde{G}_c$ APPROACH TO CYCLIC LOADING

For an arbitrarily shaped body with a through-the-thickness crack of length  $c$ , at any instant of slow crack growth, a global energy balance criterion has been written as [7,8],

$$\frac{\partial}{\partial c} (W-U) = \frac{\partial}{\partial c} (W-U'-U'') = \frac{\partial \Gamma}{\partial c}, \quad (1)$$

in which  $W$  = external work energy,  
 $U = U' + U''$  = total deformation energy,  
 $U'$  = elastic deformation energy,  
 $U''$  = plastic deformation energy, and  
 $\Gamma$  = fracture surface energy.

From this equality a general definition for nonlinear energy toughness has been obtained as

$$\tilde{G}_c = \frac{\partial}{\partial c} (W-U'-U'') = \left. \frac{\partial \Gamma}{\partial c} \right|_{\text{crit}}. \quad (2)$$

This definition is valid regardless of whether the material exhibits a linear or nonlinear behavior during fracture toughness testing. From this general definition an expression for fracture toughness has been given [7], which can be easily evaluated from conventional fracture toughness test data.

The load-displacement record obtained from a fracture toughness test is a curve comprised of a linear and a nonlinear

portion, which can be represented by a Ramberg-Osgood relation

$$v = \frac{F}{M} + k \left(\frac{F}{M}\right)^n, \quad (3)$$

where  $v$  = displacement

$F$  = load

$M$  = initial slope, and

$n$  and  $k$  are constants for a given test curve. From this relation and eq. (2) an expression for the nonlinear energy toughness  $\tilde{G}_c$  can be obtained as

$$\tilde{G}_c = \tilde{C} \bar{G}_c, \quad (4)$$

$$\text{in which } \bar{G}_c = \frac{F^2}{2B} \frac{\partial(1/M)}{\partial c} \Big|_{\text{crit}} \quad (5)$$

is the linear portion of the critical strain energy release rate at the onset of unstable fracture, and

$$\tilde{C} = \left[ 1 + \frac{2nk}{n+1} \left(\frac{F}{M}\right)^{n-1} \right] \quad (6)$$

is a measure of the nonlinearity of the load-displacement record. Although other procedures could have been used,  $\bar{G}_c$  was obtained from the relation  $\bar{G}_c = \frac{K_c^2}{E}$ . For center-cracked specimens as shown in Fig. 1,  $K_c$  was determined from the ASTM formula

$$K_c = \sigma_c \left(\frac{\pi c}{2}\right)^{\frac{1}{2}} \left[ 1 - 0.1 \left(\frac{c}{w}\right) + \left(\frac{c}{w}\right)^2 \right]^2. \quad (7)$$

The procedure for determining  $\tilde{C}$  from the load-displacement curve is described in Ref. [14].

Although eq. (4) is strictly applicable only when there is no subcritical crack growth, it has been found experimentally [11] that, even when subcritical crack growth occurs, determination of  $\tilde{G}_c$  from the entire load-displacement record up to the initiation of unstable fracture gives good results. The nonlinear energy method has also been applied to cyclic tension-tension loadings in which each load peak exceeded the previous one according to an exponential function [13]. In this work the cyclic nonlinear energy toughness,  $\tilde{G}_{fc}$ , was not determined from individual load excursions but from an envelope of all cyclic curves prior to unstable fracture. Since the unloading and reloading curves follow essentially the same path, as illustrated in Fig. 2, it is apparent that no major inelastic processes are occurring during this unload-reload cycle. Of course, minor damage accumulation is occurring in each cycle, so the cumulative effect can be incorporated into the envelope of the individual cyclic curves. This procedure was used for a limited number of tests on 2024-T3 and 7075-T6 aluminum alloys. Based on the knowledge gained in the earlier research [13], this procedure is examined further in this report.

### EXPERIMENTAL PROCEDURE

In this research program, a number of cyclic loading tests were performed on center-cracked sheets of 7075-T6 aluminum alloy. These specimens were made from 0.063 in. (1.6 mm) thick sheets with the length,  $L = 30.0$  in. (762 mm), gauge length,  $GL = 27.0$  in. (686 mm), width,  $w = 12.0$  in. (305 mm), and crack length-to-width ratio,  $c/w = 0.5$ . The notches were made by milling and were subsequently sharpened to a notch-tip radius of 0.003 - 0.005 in. (0.07 - 0.13 mm) with the use of a screw head file. To measure subcritical crack growth, the region ahead of the notch-tip was coated with a thin layer of Dykem layout blue and lines perpendicular to the notch were scribed at an interval of 0.050 in. (1.27 mm). Observations of the crack growth were facilitated by the use of a hand-held magnifier (10x). Using this procedure it was possible to measure crack growth to an accuracy of 0.005 in. (0.13 mm).

The cyclic loads were applied according to the relation

$$F_n = F_o (1 - e^{-nx}) \quad (8)$$

where  $F_o$  = estimated fracture load in monotonic loading,  
 $n$  = cycle number,  
 $x$  = increment per cycle, and  
 $F_n$  = the load corresponding to cycle number  $n$ .

Since most of the load cycles for any value of  $n$  are applied at the upper range of load levels, their effect on crack-tip plasticity and subcritical crack growth is maximized. Different load increments have been employed through selection of different values of  $x$  so that the variation in  $\tilde{G}_{fc}$  was obtained as a function of the number of cycles to failure, as was previously done for the 2024-T3 aluminum alloy sheets [13]. The tests were carried out with values of  $x$  varying from infinity (monotonic loading) to 0.001. The tests were performed on an MTS machine operated in load control. For each cycle the specimen was loaded in 20 seconds and unloaded in 10 seconds. The load-displacement curves were recorded on an X-Y recorder and the envelope of all of the cyclic curves was used to determine  $\tilde{G}_{fc}$ .

#### RESULTS AND DISCUSSION

Decreasing the load increment,  $x$ , causes a decrease in the rate of increase in load per cycle, and hence an increase in the number of cycles to failure. The variation of  $\tilde{G}_{fc}$  as a function of the number of cycles to failure,  $N$ , is seen in Fig. 3. The  $\tilde{G}_{fc}$  values corresponding to  $N = 1$  ( $x = \infty$ ) were taken from monotonic loading tests conducted earlier. The values of  $\tilde{G}_{fc}$  exhibited a tendency to decrease with increasing cyclic life. As was seen for 2024-T3 [13] the decrease was approximately a linear logarithmic function of the cyclic life in

the initial portion, but the decrease in load in the higher cycle range was faster and started to deviate from a straight line. The curve had the appearance of a compressed S-N curve, with the number of cycles to failure being much smaller than in the unnotched test because the crack initiation phase is suppressed in the notched specimens. The variation in the crack growth behavior with  $x$  is illustrated in Fig. 4, where it is seen that the amount of cyclic crack growth increased with decreasing load increment.

It was noted that more scatter appeared in 7075-T6 toughness values than in the 2024-T3 alloy. This was also observed in the static fracture toughness testing of these alloys, and is generally attributed to the increased brittle nature of the 7075-T6 alloy. The specimen which failed after 812 cycles had a much larger toughness than other specimens of the same order of cyclic lives. The fracture surface of this specimen was unique. Whereas all the other specimens failed with a full slant fracture surface, the fracture surface of this specimen had a double slant face and a square rupture region at the center of the thickness. The higher cyclic toughness of this specimen is attributed to this difference in fracture mode. It was also seen that the rate of decrease in cyclic fracture toughness with increasing cyclic life was greater for 2024-T3 than for 7075-T6 in the range in which both the alloys were tested. This implies that 2024-T3, in the presence of cracks, is more sensitive to fatigue loading

than 7075-T6, and is opposite to the usually held view. However 2024-T3 was tested only in a smaller cycle range than 7075-T6, and further testing would be needed to confirm this observation.

### CONCLUSIONS

The nonlinear energy toughness was evaluated as a failure criterion in cyclic loading of 7075-T6 aluminum alloy. The cyclic nonlinear energy toughness,  $\tilde{G}_{fc}$  was found to decrease with increasing cyclic life in a manner similar to a compressed classical S-N diagram. This trend is similar to that observed earlier in the 2024-T3 alloy, but the rate of decrease in  $\tilde{G}_{fc}$  with increasing cyclic life was lower for the more brittle 7075-T6 than the ductile 2024-T3, which contrasts with the usually held view that the former is more sensitive to fatigue loading than the latter.

LIST OF REFERENCES

- [1] Fracture Toughness Evaluation by R Curve Methods, STP 527, Am. Soc. Testing and Materials, 1973.
- [2] J. R. Rice, A Path Independent Integral and the Approximate Analysis of Strain Concentration by Notches and Cracks. J. Appl. Mech. p. 379, 1968.
- [3] J. A. Begley and J. D. Landes, The J Integral as a Fracture Criterion. Fracture Toughness, STP 514, Am. Soc. Testing and Materials, 1972.
- [4] A. A. Wells, Unstable Crack Propagation in Metals. Proc. Conf. Crack Propagation, Cranfield, England, p. 210, 1962.
- [5] J. D. Landes and J. A. Begley, Test Results From J Integral Studies -- An Attempt to Establish a  $J_{Ic}$  Testing Procedure. Fracture Analysis, STP 560, Am. Soc. Testing and Materials, pp. 170-186, 1974.
- [6] R. W. Nichols, et al., The Use of Critical COD Techniques for the Selection of Fracture Resistant Materials. Pract. Fract. Mech. for Struct. Steel, Chapman and Hall/UKAEA, Risley, England, 1969.
- [7] J. Eftis, D. L. Jones and H. Liebowitz, On Fracture Toughness in the Nonlinear Range. Engrg. Fract. Mech., Vol. 7, pp. 491-504, 1975.

- [8] J. Eftis, and H. Liebowitz, On Fracture Toughness Evaluation for Semibrittle Fracture. Engrg. Fract. Mech., Vol. 7, pp. 101-136, 1975.
- [9] D. L. Jones, P. K. Poulouse and H. Liebowitz, A Comparison of the Effect of Specimen Thickness and Subcritical Crack Growth on Several Nonlinear Fracture Toughness Parameters. Proc. Sec. Int'l. Conf. on Mechanical Behavior of Mat'ls., Boston, pp. 1252-1257, 1976.
- [10] H. Liebowitz, D. L. Jones and P. K. Poulouse, Development of the Nonlinear Energy Method for Determination of Fracture Toughness Values. Prospects of Fracture Mechanics, ed. by Sih, van Elst and Broek, Noordhoff, pp. 103-123, 1974.
- [11] D. L. Jones, P. K. Poulouse, J. Eftis and H. Liebowitz. An Investigation of Nonlinear Fracture Toughness in Aluminum Alloys Under Plane Stress Conditions.
- [12] H. S. Lamba, The J-Integral Applied to Cyclic Loading. Engrg. Fract. Mech., Vol. 7, pp. 693-703, 1975.
- [13] P. K. Poulouse, D. L. Jones and H. Liebowitz, Determination of Nonlinear Energy Toughness Value for Cyclic Loading Applications. Engrg. Fract. Mech., Vol. 8, pp. 293-299, 1976.
- [14] H. Liebowitz and D. L. Jones, On Test Methods for Nonlinear Fracture Mechanics, Tenth Anniv. Mtg. Soc. Engrg. Sci., Raleigh, NC, 1973.

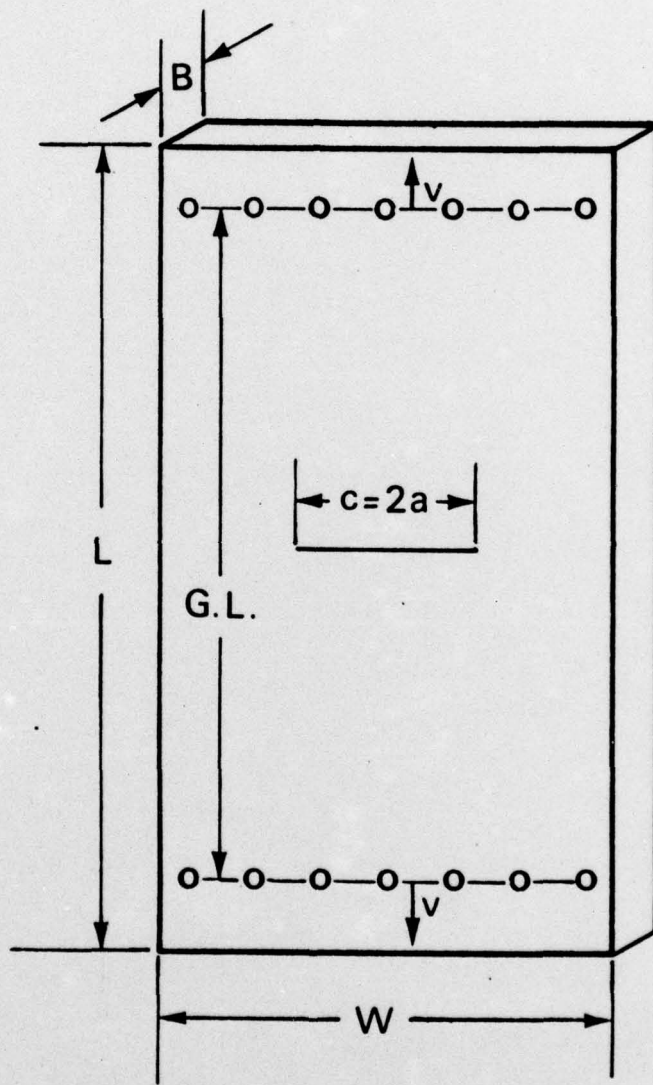


Fig. 1. General specimen geometry

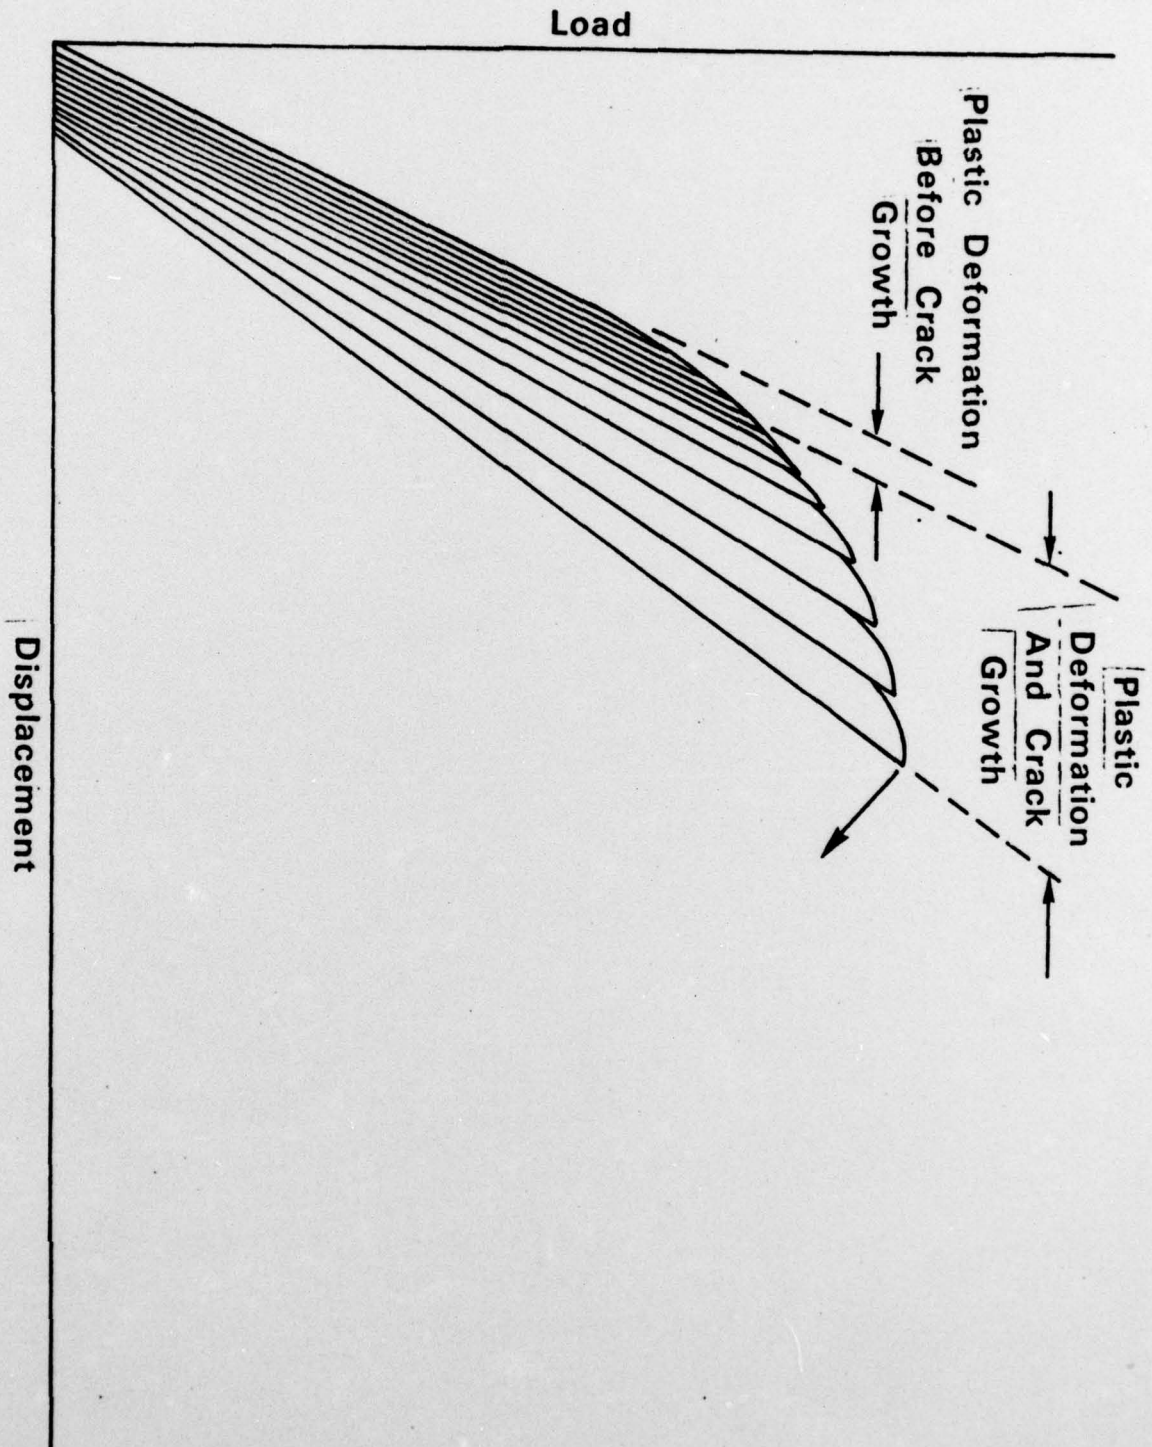


Fig. 2 A schematic representation of load-displacement curves in cyclic loading

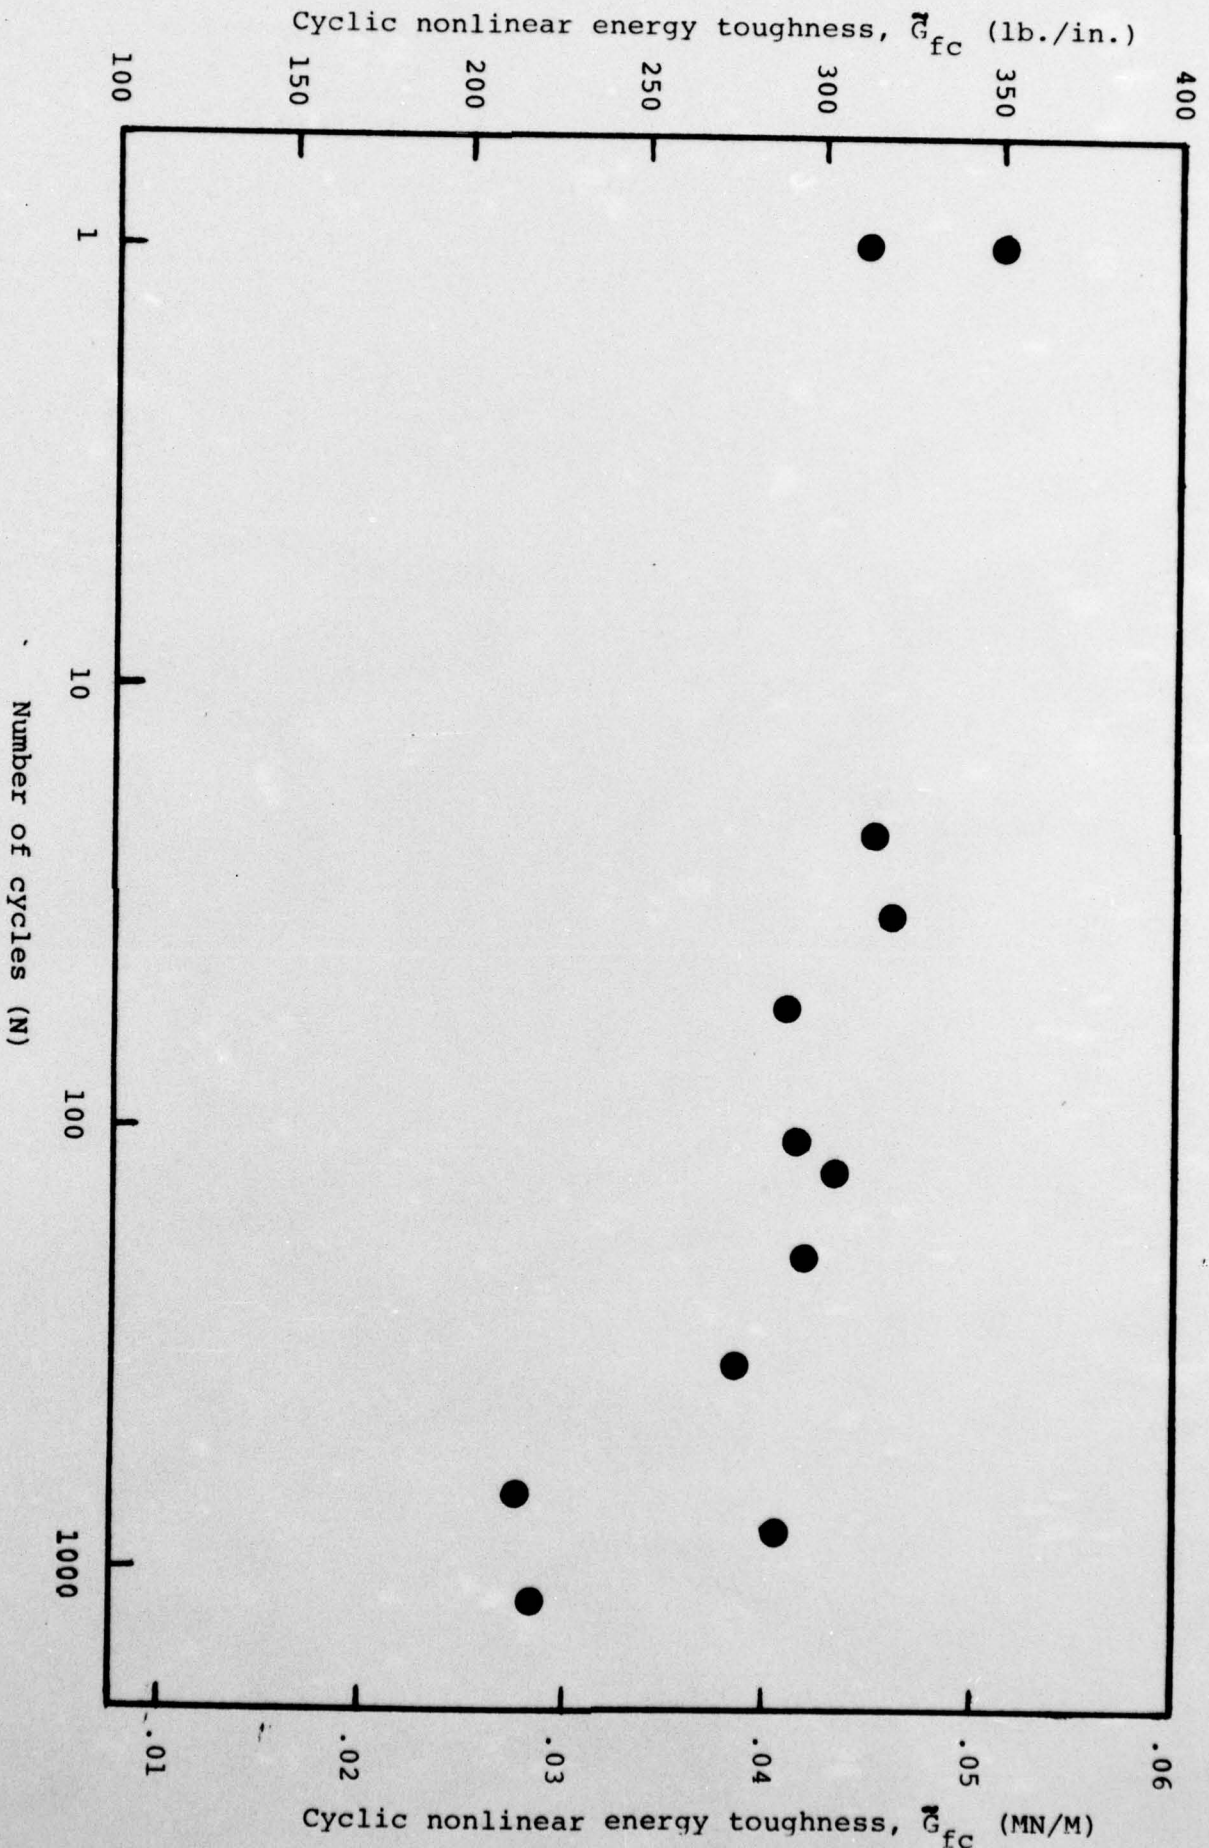


Fig. 3. Variation of cyclic nonlinear energy toughness with number of load cycles to failure in 7075-T6 alloy.

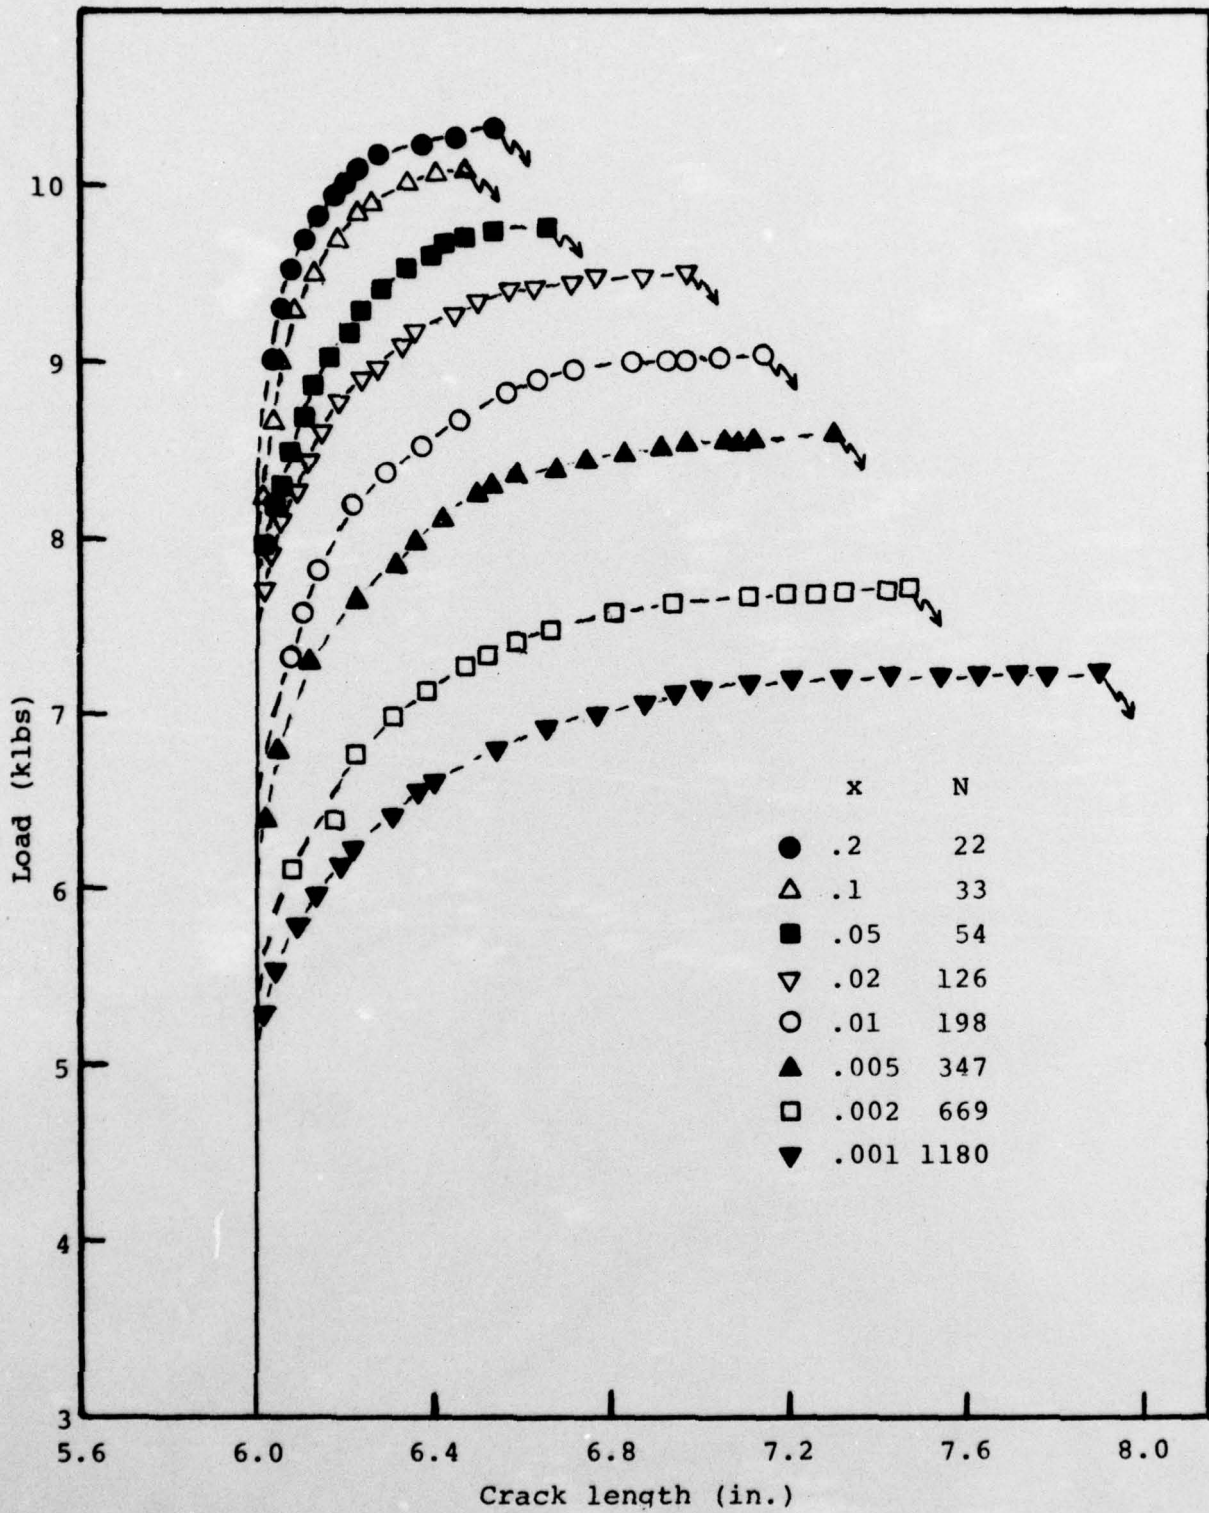


Fig.4. Crack growth curves for different cyclic load increments in 7075-T6 alloy.

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM	
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER	
		9) Final	
4. TITLE (and Subtitle)		5. TYPE OF REPORT & PERIOD COVERED	
6) DETERMINATION OF CYCLIC NONLINEAR ENERGY TOUGHNESS FOR 7075-T6 ALUMINUM SHEETS.		Technical Report.	
7. AUTHOR(S)		8. CONTRACT OR GRANT NUMBER(s)	
10) P. K. Poulose, D. L. Jones and H. Liebowitz		15) N00019-76-C-0151 new	
9. PERFORMING ORGANIZATION NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS	
School of Engineering and Applied Science The George Washington University Washington, D. C. 20052			
11. CONTROLLING OFFICE NAME AND ADDRESS		11) 16. REPORT DATE	
Naval Air Systems Command Department of the Navy Washington, D. C. 20361		Dec 1976	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		13. NUMBER OF PAGES	
12) 22p.			
		15. SECURITY CLASS. (of this report)	
		Unclassified	
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report)			
Approved for public release: Distribution Unlimited			
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)			
18. SUPPLEMENTARY NOTES			
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)			
Fracture toughness      Nonlinear response Cyclic loading          Crack growth			
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)			
In this report, the non-linear energy method for fracture toughness determination has been applied to cyclic loading conditions. The nonlinear energy toughness for cyclic loading, $G_{(c)}$ , was obtained from an envelope of the cyclic load-displacement record for thin center-cracked sheet specimens of 7075-T6 aluminum alloy. A cyclic loading program, in which each succeeding load peak approached the static load in an exponential manner, was applied to these specimens. With constant specimen dimensions, different load increments were used for different			

JP

↓  
specimens, which resulted in varying cyclic lives.

↖ The specimens used in these tests exhibited a significant reduction in  $G_{fd}$  with increasing cyclic life in a manner analogous to the classical S-N diagram. This reduction in life for 7075-T6 was significantly less than for 2024-T3, which had been evaluated previously although 2024-T3 has considerably higher toughness.  
↑

**THE GEORGE WASHINGTON UNIVERSITY**

**BENEATH THIS PLAQUE  
IS BURIED  
A VAULT FOR THE FUTURE  
IN THE YEAR 2036**

**THE STORY OF ENGINEERING IN THIS YEAR OF THE PLACING OF THE VAULT AND  
ENGINEERING HOPES FOR THE TOMORROWS AS WRITTEN IN THE RECORDS OF THE  
FOLLOWING GOVERNMENTAL AND PROFESSIONAL ENGINEERING ORGANIZATIONS AND  
THOSE OF THIS GEORGE WASHINGTON UNIVERSITY.**

**BOARD OF COMMISSIONERS DISTRICT OF COLUMBIA  
UNITED STATES ATOMIC ENERGY COMMISSION  
DEPARTMENT OF THE ARMY UNITED STATES OF AMERICA  
DEPARTMENT OF THE NAVY UNITED STATES OF AMERICA  
DEPARTMENT OF THE AIR FORCE UNITED STATES OF AMERICA  
NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS  
NATIONAL BUREAU OF STANDARDS U.S. DEPARTMENT OF COMMERCE  
AMERICAN SOCIETY OF CIVIL ENGINEERS  
AMERICAN INSTITUTE OF ELECTRICAL ENGINEERS  
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS  
THE SOCIETY OF AMERICAN MILITARY ENGINEERS  
AMERICAN INSTITUTE OF MINING & METALLURGICAL ENGINEERS  
DISTRICT OF COLUMBIA SOCIETY OF PROFESSIONAL ENGINEERS, INC.  
THE INSTITUTE OF RADIO ENGINEERS, INC.  
THE CHEMICAL ENGINEERS CLUB OF WASHINGTON  
WASHINGTON SOCIETY OF ENGINEERS  
FAULKNER KINGSBURY & STENHOUSE - ARCHITECTS  
CHARLES H TOMPKINS COMPANY - BUILDERS  
SOCIETY OF WOMEN ENGINEERS  
NATIONAL ACADEMY OF SCIENCES, NATIONAL RESEARCH COUNCIL**

**THE PURPOSE OF THIS VAULT IS INSPIRED BY AND IS DEDICATED TO  
CHARLES HOOK TOMPKINS, DOCTOR OF ENGINEERING  
BECAUSE OF HIS ENGINEERING CONTRIBUTIONS TO THIS UNIVERSITY, TO HIS  
COMMUNITY, TO HIS NATION AND TO OTHER NATIONS.**

**BY THE GEORGE WASHINGTON UNIVERSITY.**

**ROBERT V. FLEMING  
CHAIRMAN OF THE BOARD OF TRUSTEES**

**CLOYD H. MARVIN  
PRESIDENT**

**JUNE THE TWENTIETH  
1955**

To cope with the expanding technology, our society must be assured of a continuing supply of rigorously trained and educated engineers. The School of Engineering and Applied Science is completely committed to this objective.