

AD-A042 044

CALIFORNIA UNIV BERKELEY DEPT OF CHEMICAL ENGINEERING
VISCOELASTIC PROPERTIES OF HOMOGENEOUS BLOCK COPOLYMERS.(U)
MAY 77 M SHEN, D SOONG, D R HANSEN

F/G 7/3


N00014-75-C-0955

UNCLASSIFIED

TR-13

NL

| OF |
AD
A042 044



END

DATE
FILMED
8-77

AD A 042044

Technical Report No. 13

12
NW

VISCOELASTIC PROPERTIES OF HOMOGENEOUS
BLOCK POLYMERS

by

M. Shen and D. Soong
Department of Chemical Engineering
University of California
Berkeley, California 94720

and

D. R. Hansen
Shell Development Company
Houston, Texas 77001

May 15, 1977

Technical Report to be published in
Polymer Engineering and Science

Approved for public release: Distribution Unlimited

Prepared for
Office of Naval Research
800 North Quincy Street
Arlington, Virginia 22217

AD No. _____
DDC FILE COPY

47
DDC
RECEIVED
JUL 27 1977
RECEIVED
F

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) 6 Viscoelastic Properties of Homogeneous Block Copolymers.		5. TYPE OF REPORT & PERIOD COVERED 9 Technical Report.
7. AUTHOR(s) 10 M. Shen, D. Soong and D. R. Hansen		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemical Engineering University of California Berkeley, California 94720		8. CONTRACT OR GRANT NUMBER(s) 13 14 N0001e-75-C-0955
11. CONTROLLING OFFICE NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
12. REPORT DATE 11 15 May 1977		13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 16p. 14 TR-13		15. SECURITY CLASS. (of this report)
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release: Distribution unlimited 15 N00014-75-C-0955		18a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Block Copolymers, Viscoelasticity		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The molecular theory of Rouse-Bueche-Zimm has been modified to predict the viscoelastic behavior of homogeneous block copolymers. The model consists of beads and springs whose magnitudes correspond to the types of blocks in the polymer. Maximum relaxation times can be computed by this model. Viscoelastic data for poly(styrene-b- α -methylstyrene- alpha		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

104 601

13

alpha
b-styrene), poly(α -methylstyrene-b-styrene-b- α -methylstyrene) and poly(styrene-b- α -methylstyrene) were determined by stress relaxation methods. The results compare favorably with those predicted by the theory.

ACCESSION for	
NTIS	White Section ☒
DDC	Buff Section ☐
UNANNOUNCED	☐
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	AvAIL. and/or SPECIAL
A.	

VISCOELASTIC PROPERTIES OF HOMOGENEOUS
BLOCK COPOLYMERS

by

M. Shen and D. Soong
Department of Chemical Engineering
University of California
Berkeley, California 94720

and

D. R. Hansen
Shell Development Company
Houston, Texas 77001

ABSTRACT

The molecular theory of Rouse-Bueche-Zimm has been modified to predict the viscoelastic behavior of homogeneous block copolymers. The model consists of beads and springs whose magnitudes correspond to the types of blocks in the polymer. Maximum relaxation times can be computed by this model. Viscoelastic data for poly(styrene-*b*- α -methylstyrene-*b*-styrene), poly(α -methylstyrene-*b*-styrene-*b*- α -methylstyrene) and poly(styrene-*b*- α -methylstyrene) were determined by stress relaxation methods. The results compare favorably with those predicted by the theory.

INTRODUCTION

It is well known that most block copolymers show microphase separation as a consequence of their positive free energy of mixing between the polymeric blocks¹. These heterophase polymers have been found to exhibit many unique properties that are dramatically different from those of the homogeneous polymers². However, a limited number of block copolymers have shown no microphase separation, for example the styrene/ α -methyl styrene system³. The viscoelastic properties of these homogeneous block copolymers are amenable to theoretical treatment by the bead-and-spring model enunciated by Rouse⁶, Bueche⁷, and Zimm⁸ (the RBZ model). In this paper, we shall discuss the molecular theory of viscoelasticity for homogeneous block copolymers⁹⁻¹³. The results of the calculations are compared with the experimental data on the diblock and triblock copolymers of styrene and α -methyl styrene^{13,14}.

THEORY

The RBZ model represents the polymer molecule by replacing the N submolecules with $N+1$ beads held together with N entropy springs. When the polymer coil is disturbed by a velocity gradient, the springs are stretched. The restoring force of these entropy springs is proportional to displacement, the spring constant being given by $3kT/b^2$ where b^2 is the average square end-to-end distance of the submolecule. As the beads move through the medium, a viscous drag is exerted on them whose magnitude is determined by the friction coefficient

f. As the flow ceases, the recovery of the polymer chain is effected without acceleration, so that the viscous and the elastic forces are exactly equal to each other.

For homopolymers, all of the beads in the model have identical spring constants and frictional coefficients. In the case of block copolymers, both of these parameters are expected to be different for different blocks in the polymer. For example, the equations of motion for an SAS triblock copolymer can be written as⁹:

$$\dot{\underline{x}} = -\sigma_S \underline{D}^{-1} \underline{Z} \underline{x} \quad (1)$$

In eq. 1, $\underline{x}$ and $\dot{\underline{x}}$ are column vectors of bead positions and velocities respectively, $\underline{Z}$ is the nearest neighbor matrix, and $\sigma_S = 3kT/b_S^2 f_S$ where k is Boltzmann constant, T is the absolute temperature, b_S^2 is the mean square end-to-end distance and f_S is frictional coefficient. $\underline{D}^{-1}$ is the inverse of the following matrix

$$\underline{D} = \begin{bmatrix} & & & & \bigcirc \\ & 1 & & & \\ & & \ddots & & \\ & & & \delta_A & \\ & & & & \delta_A \\ & & & & & \ddots \\ & & & & & & 1 \\ \bigcirc & & & & & & & 1 \end{bmatrix} \quad (2)$$

where

$$\delta_A = b_A^2 f_A / b_S^2 f_S = a_A^2 m_A^2 \zeta_A / a_S^2 m_S^2 \zeta_S \quad (3)$$

In eq. 3, m is the number of monomer units per submolecule, a is the characteristic length, ζ is the monomeric friction coefficient, and $b^2 = ma^2$. Subscripts A and S refer to A-blocks and S-blocks respectively.

To solve eq. 3, we define a new set of coordinates $\underline{r}$ related to $\underline{x}$ through

$$\underline{r} = \underline{A} \underline{x}, \quad (4)$$

where the $\underline{A}$ matrix is defined by $\underline{Z} = \underline{A}^T \underline{A}$. Operating on both sides of eq. 1 with $\underline{A}$, we get

$$\begin{aligned} \underline{\ddot{r}} &= \sigma_A \underline{A} \underline{D}^{-1} \underline{A}^T \underline{A} \underline{x} \\ &= -\sigma_A \underline{S} \underline{r}, \end{aligned} \quad (5)$$

where

$$\underline{S} = \underline{A} \underline{D}^{-1} \underline{A}^T \quad (6)$$

is a symmetrical tridiagonal $N \times N$ matrix which differs from the well known Rouse matrix⁶ ($\underline{R} = \underline{A} \underline{A}^T$) by the extra operation $\underline{D}^{-1}$. For a homopolymer, all of the elements in our $\underline{D}$ matrix are unity, and the $\underline{S}$ matrix is reduced to the $\underline{R}$ matrix.

The eigenvalue spectrum (λ_p 's) of the $\underline{S}$ matrix is readily obtained by numerical methods on a computer⁹. In order that the results are not functions of the matrix sizes (number of beads), we use the following expression in computing from the eigenvalues the normalized retardation times:

$$\tau_p(\text{normalized}) = 1/(N+1)^2 \lambda_p \quad (7)$$

transition temperatures (100°C and 167°C). The glass transition temperature is chosen as the reference state for comparing the monomeric friction coefficients because it is preferable to compare the ζ 's at equivalent states of molecular motion as would be the case in a homogeneous copolymer. Using these values in eq. 3, we find¹³ that

$$\delta_A = 423.$$

A matrix with 140 beads was used to compute the maximum relaxation time for 100% S beads. In calculating τ_M for the copolymers the molecular weight must remain fixed for a meaningful comparison. For simplicity the monomer molecular weight of styrene will be set to equal to that of α -MS. Thus

$$N_S + N_A \left(\frac{m_A}{m_S} \right) = 140 \quad (9)$$

where N_A and N_S are the number of PS and P α MS beads. Therefore the total number of beads in the chain ($N_A + N_S$) will decrease as the weight percent of α -MS increases.

$$\text{wt. \% } \alpha\text{-MS} = N_A m_A / (N_S m_S + N_A m_A) \quad (10)$$

The computed maximum relaxation times are given in Table 1. They are reduced by the maximum relaxation computed for PS (τ_m^0) for ease of comparison.

In order to compare with the theoretical results, block copolymers of styrene (S) and α -methylstyrene (A) were chosen for experimentation. Five triblock copolymers of poly(styrene-

b- α -methylstyrene-b-styrene) or SAS are synthesized by the anionic technique¹³. In addition, one each of poly(α -methylstyrene-b-styrene-b- α -methylstyrene)¹³ or ASA, and poly(α -methylstyrene-b-styrene)¹⁴, or AS, were used. Stress relaxation techniques were used to generate viscoelastic master curves by the Time-Temperature Superposition Principle^{13,14}. Distribution of relaxation times can be readily computed from the master curves by well known methods¹⁶. One such example for the SA block polymer¹⁴ is shown in Fig. 1.

To assure the homogeneous nature of these block copolymers, dynamic mechanical experiments were carried out. If the samples indeed show no microphase separation, then only one primary glass transition will be observed. A representative curve for SA sample⁴ is shown in Fig. 2. Here we see that there is only one loss tangent peak rather than two. Similar data have been reported for the other block copolymers^{13,14}. Fig. 2 also shows the dynamic storage moduli data for the sample⁴. There is a precipitous drop in the modulus near 135°C, indicating the onset of the primary glass transition of the polymer.

From the distribution of relaxation times given in Fig. 1, it is simple to compute the linear viscoelastic parameters¹⁶. We have taken advantage of this technique to calculate the G' and $\tan \delta$ for the AS block copolymer as a function of log time, then using the WLF shift factor data to transform the abscissa to temperature. The solid line shows in Fig. 2 that there is good agreement with the dynamic mechanical data.

The experimental maximum relaxation times of the block copolymers were determined from the viscoelastic master curves

by using Procedure X of Tobolsky and Murakami¹⁸. Because the maximum relaxation times are strong functions of temperature and molecular weight, these effects must be compensated for in order to make a valid comparison. We shall use $T_i + 29^\circ\text{C}$ as the reference temperature and 1.2×10^5 as the reference molecular weight. The relationship $d \ln \tau_m / d \ln M_w = 3.4$ was used to extrapolate the maximum relaxation times to the reference molecular weight. These experimental values of τ_m are given in Table 1. The maximum relaxation times were again normalized by τ_m for pure polystyrene. Since literature values^{18,19} for τ_m of pure polystyrene differ somewhat from each other, an average value of $\log \tau_m^\circ = 2.36$ (seconds) was used. As seen in Table 1, most of the normalized experimental and computed maximum relaxation times are in reasonable agreement for the SAS, ASA and AS block copolymers. The samples showing significant discrepancies are SAS with 5% and 42% α -methylstyrene. However, we note that the value of τ_m for the only ASA value in the figure is substantially higher than that of the SAS of comparable composition, as predicted by the theory.

ACKNOWLEDGEMENT

This work was supported by the Office of Naval Research, and by the Union Carbide Corporation.

REFERENCES

1. S. Krause, Rev. Macromol. Chem., 7, 251 (1972).
2. M. Shen and H. Kawai, A.I.Ch.E. J., in press.
3. M. Baer, J. Polymer Sci., A2, 417 (1964).
4. L. M. Robeson, M. Matzner, L. J. Fetters, and J. E. McGrath, in "Recent Advances in Polymer Blends, Grafts, and Blocks," L. H. Sperling, ed., Plenum, New York, p.281.
5. M. Shen and D. R. Hansen, J. Polymer Sci., Part C, 46, 55 (1974).
6. P. E. Rouse, J. Chem. Phys., 21, 1272 (1953).
7. F. Bueche, J. Chem. Phys., 22, 603 (1954).
8. B. Zimm, J. Chem. Phys., 24, 269 (1956).
9. D. R. Hansen and M. Shen, Macromolecules, 8, 343 (1975).
10. W. F. Hall and R. E. DeWames, Macromolecules, 8, 349 (1975).
11. W. H. Stockmayer and J. W. Kennedy, Macromolecules, 8, 351 (1975).
12. F. W. Wang, Macromolecules, 8, 364 (1975).
13. D. R. Hansen, and M. Shen, Macromolecules, 8, 903 (1975).
14. D. Soong and M. Shen, Macromolecules, in press.
15. K. Osaki and J. L. Schrag, Polymer J., 2, 541 (1971).
16. J. D. Ferry, "Viscoelastic Properties of Polymers", 2nd ed., Wiley, New York, 1970.
17. T. Fujimoto, N. Ozaki and M. Nagasawa, J. Polymer Sci.-Phys., 6, 129 (1968).
18. A. V. Tobolsky and K. Murakami. J. Polymer Sci., 40, 443 (1959); *ibid.*, 47, 55 (1960).
19. N. Nemoto, J. Polymer Sci., A2, 875 (1967).

Table 1. Comparison of Experimental and Theoretical
Maximum Viscoelastic Relaxation Times for Block
Copolymers of Styrene and α -Methylstyrene^{13,14}.

Sample	Wt% α MS	log (τ_m/τ_m^0)	
		Expt'l	Theor.
SAS	5	0.50	0.05
	17	0.59	0.55
	34	1.01	1.10
	42	0.89	1.50
	65	1.76	1.90
ASA	73	2.26	2.30
AS	50	1.75	1.75

FIGURE CAPTIONS

- Figure 1. Distribution of relaxation times for poly(α -methylstyrene-*b*-styrene) calculated from the viscoelastic master curve¹⁴ by the second approximation method¹⁶.
- Figure 2. Dynamic mechanical data at approximately 1 Hz as a function of temperature for poly(α -methylstyrene-*b*-styrene)⁴. Solid lines are curves computed from the stress relaxation data¹⁴ by using the distribution of relaxation times given in Figure 1.

Fig. 1

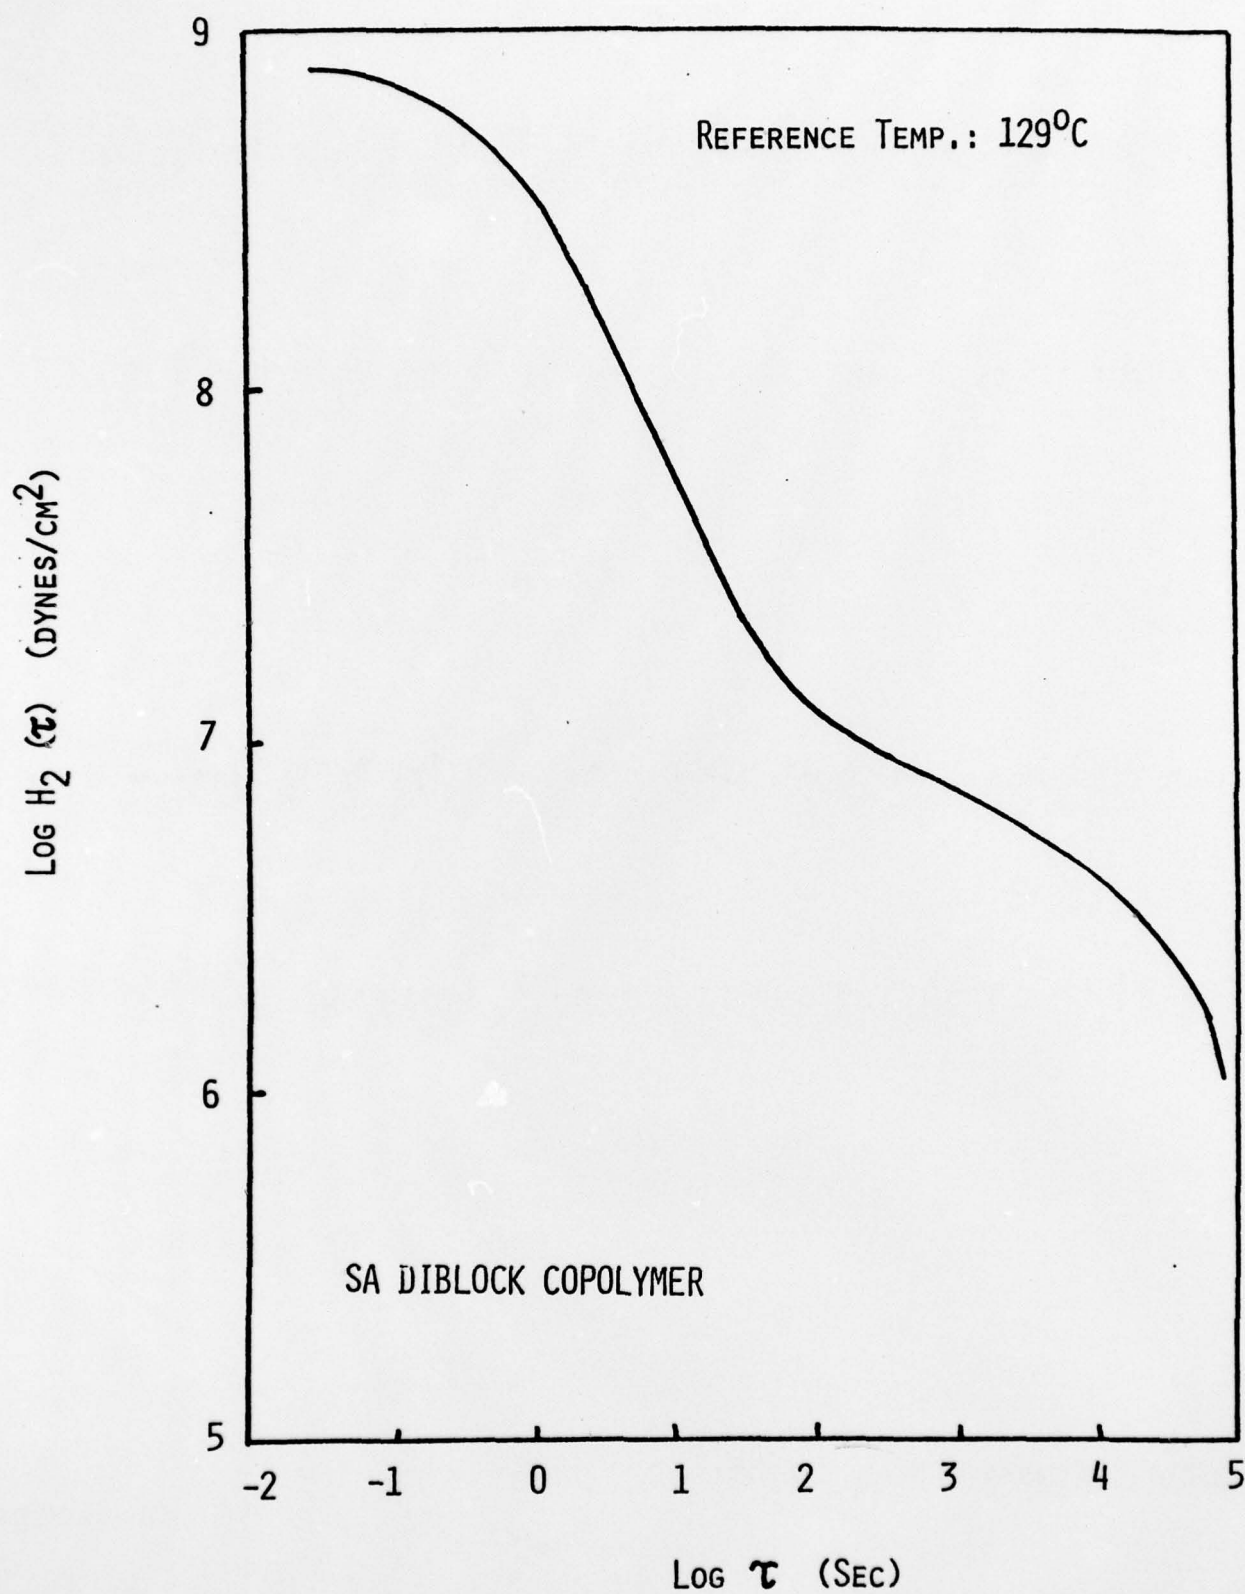


Fig. 2

