

AD-A043 742

GENERAL ELECTRIC CO CINCINNATI OHIO AIRCRAFT ENGINE GROUP F/G 21/5  
COMPRESSOR BLADE MANUFACTURE BY ELECTROCHEMICAL MACHINING. ADVA--ETC(U)  
AUG 77 W I WESTPHAL, A LINGEN F33657-72-C-0206


UNCLASSIFIED

AFAPL-TR-77-33

NL

1 OF 1  
ADA043 742



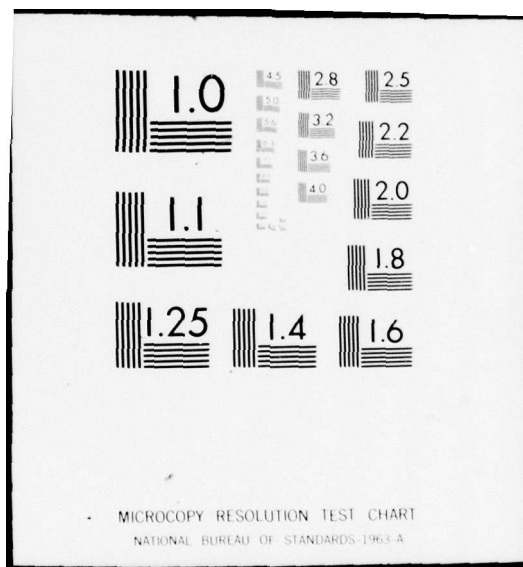

AFAPL-TR-77-33

me 2

AD A 043742

# COMPRESSOR BLADE MANUFACTURE BY ELECTROCHEMICAL MACHINING

## ADVANCED TURBINE ENGINE GAS GENERATOR

GENERAL ELECTRIC COMPANY  
✓ AIRCRAFT ENGINE GROUP  
CINCINNATI, OHIO 45215

August 1977

TECHNICAL REPORT AFAPL-TR-77-33  
Final Report for Period December 1973 - March 1977

APPROVED FOR PUBLIC RELEASE;  
DISTRIBUTION UNLIMITED

DDC  
SEP 1 1977  
RECEIVED  
C

AIR FORCE AERO PROPULSION LABORATORY  
WRIGHT AERONAUTICAL LABORATORIES  
AIR FORCE SYSTEMS COMMAND  
WRIGHT-PATTERSON AFB, OHIO 45433

AD NO.  
DDC FILE COPY

# NOTICE

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

This report has been reviewed by the Information Office, (ASD/OIP) and is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nations.

This technical report has been reviewed and is approved for publication.

Raymond N. Leo  
Name  
Project Engineer/Scientist

FOR THE COMMANDER

TLJ Sims  
Name and Title  
Technical Area Manager  
System Engine Technology

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| REPORT DOCUMENTATION PAGE                                                                                                                                                                                                                                                                                                                                                                                                                              |                                 | READ INSTRUCTIONS<br>BEFORE COMPLETING FORM                                                           |
|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------|-------------------------------------------------------------------------------------------------------|
| 1. REPORT NUMBER<br><u>18</u> AFAPL-TR-77-33                                                                                                                                                                                                                                                                                                                                                                                                           | 2. GOVT ACCESSION NO. <u>19</u> | 3. RECIPIENT'S CATALOG NUMBER                                                                         |
| 4. TITLE (and Subtitle)<br><u>6</u> COMPRESSOR BLADE MANUFACTURE BY ELECTRO-CHEMICAL MACHINING; <del>(SECRET)</del> .<br><u>Advanced Turbine Engine Gas Generator.</u>                                                                                                                                                                                                                                                                                 |                                 | 5. TYPE OF REPORT & PERIOD COVERED<br><u>9</u> Final Technical Report.<br>December 1973 - March 1977. |
| 7. AUTHOR(s)<br><u>10</u> W.I. Westphal and A. Lingen                                                                                                                                                                                                                                                                                                                                                                                                  |                                 | 6. PERFORMING ORG. REPORT NUMBER                                                                      |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS<br>✓ Aircraft Engine Group (AE&TPD)<br>General Electric Company<br>Evendale, Ohio 45215                                                                                                                                                                                                                                                                                                                    |                                 | 8. CONTRACT OR GRANT NUMBER(s)<br><u>15</u><br>F33657-72-C-0206                                       |
| 11. CONTROLLING OFFICE NAME AND ADDRESS<br>Aero-Propulsion Laboratories (TBP)<br>Wright-Patterson AF Base, Dayton, Ohio 45433                                                                                                                                                                                                                                                                                                                          |                                 | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS<br>Task 63216F<br>Work Unit 681B0101B     |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)<br><u>16</u> <u>681B</u><br><u>12</u> <u>01</u>                                                                                                                                                                                                                                                                                                                            |                                 | 12. REPORT DATE<br><u>11</u> August 1977                                                              |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                        |                                 | 13. NUMBER OF PAGES<br>48 <u>12</u> <u>61p</u>                                                        |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                        |                                 | 15. SECURITY CLASS. (of this report)<br>Unclassified                                                  |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                        |                                 | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE                                                            |
| 16. DISTRIBUTION STATEMENT (of this Report)<br><br>Approved for Public Release; Distribution Unlimited                                                                                                                                                                                                                                                                                                                                                 |                                 |                                                                                                       |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)<br><br>DDC<br>SEP 1 1977                                                                                                                                                                                                                                                                                                                                    |                                 |                                                                                                       |
| 18. SUPPLEMENTARY NOTES                                                                                                                                                                                                                                                                                                                                                                                                                                |                                 |                                                                                                       |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number)<br><br>Compressor Blade Manufacture, Electrochemical Machining                                                                                                                                                                                                                                                                                                      |                                 |                                                                                                       |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number)<br><br>Compressor blades for the ATEGG GE14 engine were manufactured using electrochemical machining to form the airfoils. Elaborate dimensional inspections were performed on the as-machined surfaces. The blades were tested for frequency, nodal patterns, and fatigue strength and were compared to control blades made by conventional methods.<br><br>403 462 |                                 |                                                                                                       |

# FOREWORD

The work of this study was performed by the General Electric Company's Aircraft Engine Group, Cincinnati, Ohio 45215, under Contract F33657-72-C-0206 with the USAF Aero Propulsion Laboratory (TBP), Wright-Patterson AF Base, Dayton, Ohio 45433. The AF Project Monitor was Raymond N. Leo.

The technical effort was begun in December 1973 and extended through March 1977.

PRECEDING PAGE BLANK-NOT FILMED

|                                 |                                                   |
|---------------------------------|---------------------------------------------------|
| ACQUISITION FOR                 |                                                   |
| WIS                             | White Section <input checked="" type="checkbox"/> |
| QMC                             | Buff Section <input type="checkbox"/>             |
| UNCLASSIFIED                    | <input type="checkbox"/>                          |
| JUSTIFICATION                   |                                                   |
| BY                              |                                                   |
| DISTRIBUTION/AVAILABILITY CODES |                                                   |
| Dist                            | ALL / SPECIAL                                     |
| A                               |                                                   |

## TABLE OF CONTENTS

| <u>Section</u> |                                   | <u>Page</u> |
|----------------|-----------------------------------|-------------|
| I.             | INTRODUCTION                      | 1           |
| II.            | SUMMARY                           | 4           |
| III.           | BLADE MANUFACTURE                 | 9           |
| IV.            | TESTING AND INSPECTION            | 12          |
|                | A. Dimensional Checks             | 12          |
|                | B. Frequencies and Nodal Patterns | 12          |
|                | C. Fatigue Results                | 42          |
| V.             | PROCESS STATUS                    | 52          |

# LIST OF ILLUSTRATIONS

| <u>Figure</u> |                                                                                                             | <u>Page</u> |
|---------------|-------------------------------------------------------------------------------------------------------------|-------------|
| 1.            | ATEGG Option Program.                                                                                       | 2           |
| 2.            | GE14 Compressor Blades.                                                                                     | 5           |
| 3.            | Stage 5 Geometry.                                                                                           | 13          |
| 4.            | Typical Test Setup for Natural Frequencies and Nodal Patterns.                                              | 28          |
| 5.            | Resonant Frequency Summary, Stage 2 (Part No. 4013148-502P01), Standard Deviation Versus Average Frequency. | 35          |
| 6.            | Resonant Frequency Summary, Stage 5 (Part No. 4013148-505P01), Standard Deviation Versus Average Frequency. | 36          |
| 7.            | Resonant Frequency Summary, Stage 8 (Part No. 4013148-508P01), Standard Deviation Versus Average Frequency. | 37          |
| 8.            | Resonant Frequencies and Nodal Patterns, Stage 2 Blade (Part No. 4013148-502P01), ECM Airfoil S/N 367.      | 38          |
| 9.            | Resonant Frequencies and Nodal Patterns, Stage 2 Blade (Part No. 4013148-502P01), ECM Airfoil S/N 367.      | 39          |
| 10.           | Resonant Frequencies and Nodal Patterns, Stage 2 Blade (Part No. 4013148-502P01), ECM Airfoil S/N 367.      | 40          |
| 11.           | Resonant Frequencies and Nodal Patterns, Stage 2 Blade (Part No. 4013148-502P01), ECM Airfoil S/N 367.      | 41          |
| 12.           | Fatigue Results, Stage 2 ECM Airfoil (Peened 6-10N).                                                        | 43          |
| 13.           | Fatigue Results, Stage 2 Conventional Airfoil (Peened 6-10N).                                               | 44          |
| 14.           | Fatigue Results, Stage 5 ECM Airfoil (Unpeened).                                                            | 45          |
| 15.           | Fatigue Results, Stage 5 Conventional Airfoil (Peened 6-10N).                                               | 46          |
| 16.           | Fatigue Results, Stage 5 FM R95 ECM Airfoil (Unpeened).                                                     | 47          |
| 17.           | Fatigue Results, Stage 8 ECM Airfoil (Peened 6-10N).                                                        | 48          |
| 18.           | Fatigue Results, Stage 8 Conventional Airfoil (Peened 6-10N).                                               | 49          |

LIST OF ILLUSTRATIONS, (Concluded)

| <u>Figure</u> |                                                             | <u>Page</u> |
|---------------|-------------------------------------------------------------|-------------|
| 19.           | Fatigue Results, Stages 7 and 8 ECM Airfoil (Peened 6-10N). | 50          |
| 20.           | Stage-5 R95 Blade at Various Points in the ECM Process.     | 54          |

LIST OF TABLES

| <u>Table</u> |                                                                   | <u>Page</u> |
|--------------|-------------------------------------------------------------------|-------------|
| 1.           | Summary of Fatigue Results.                                       | 5           |
| 2.           | Cost Summary.                                                     | 6           |
| 3.           | Vendor Listing.                                                   | 7           |
| 4.           | Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01. | 11          |
| 5.           | Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01. | 12          |
| 6.           | ECM'd Stage 2 Blades, Part No. 4013148-502.                       | 26          |
| 7.           | Conventional Stage 2 Blades, Part No. 4013148-502.                | 27          |
| 8.           | ECM'd Stage 5 Blades, Part No. 4013148-505.                       | 28          |
| 9.           | Conventional Stage 5 Blades, Part No. 4013148-505.                | 29          |
| 10.          | ECM'd Stage 8 Blades, Part No. 4013148-508.                       | 30          |
| 11.          | Conventional Stage 8 Blades, Part No. 4013148-508.                | 31          |

## SECTION I

### INTRODUCTION


Electrochemical machining, ECM, is a process which removes material from an electrically conductive workpiece by electrolytic action and can be likened to plating in reverse. Metal removal is accomplished by means of anodic dissolution produced by the passage of a machining current through a flowing electrolyte which separates the electrode from the workpiece. The workpiece and electrode tool are connected to a d.c. power supply with the former being positively charged and the latter, negative. When an electrolyte (usually a saline solution) is pumped through the cutting gap and a current is flowing, metal is dissolved from the workpiece and into the electrolyte while the electrode tool is advanced toward the workpiece at a constant rate.

The cutting gap between the electrode tool and the workpiece is controlled by the magnitude of the voltage applied, and can be varied from 0.001-inch to 0.030-inch (practical range). The smaller the gap, the more closely the workpiece will be to a mirror image of the electrode tool. The most commonly used gaps are from 0.005-inch to 0.010-inch, which is close enough to insure a practical reproduction of the tool geometry in the workpiece.

The entire electrolytic cell is enclosed in a flow chamber or box, suitably sealed to permit the tool to be fed into the workpiece and at the same time, prevent leakage of the electrolyte. Normally, this flow box is designed so as to provide flow passages to and from the working gap. This gives greater control over the fluid flow which can be used to great advantage during Electromechanical Machining.

The advantages of the ECM process include potential cost reductions for typical blade materials, the production of geometrically more consistent parts and resulting blade dynamic characteristics which should be more consistent. Further, blades can be made from a wider variety of materials, since ECM is fairly insensitive to the material being machined.

A task of the ECM manufacture of compressor blades was offered as Option IV to the FY 74/75 modification of ATEGG contract F33657-72-C-0206. The option was exercised in December 1973 and the work began early in 1974. The work effort is described in Paragraph 9.4 of the contract Statement of Work. Blade construction by ECM methods was to provide a full set of blades for three GE14 compressor stages, as well as a quarter set of blades for structure test comparisons with a quarter set of conventionally manufactured blades for each stage. A graphical summary of the program is presented in Figure 1.

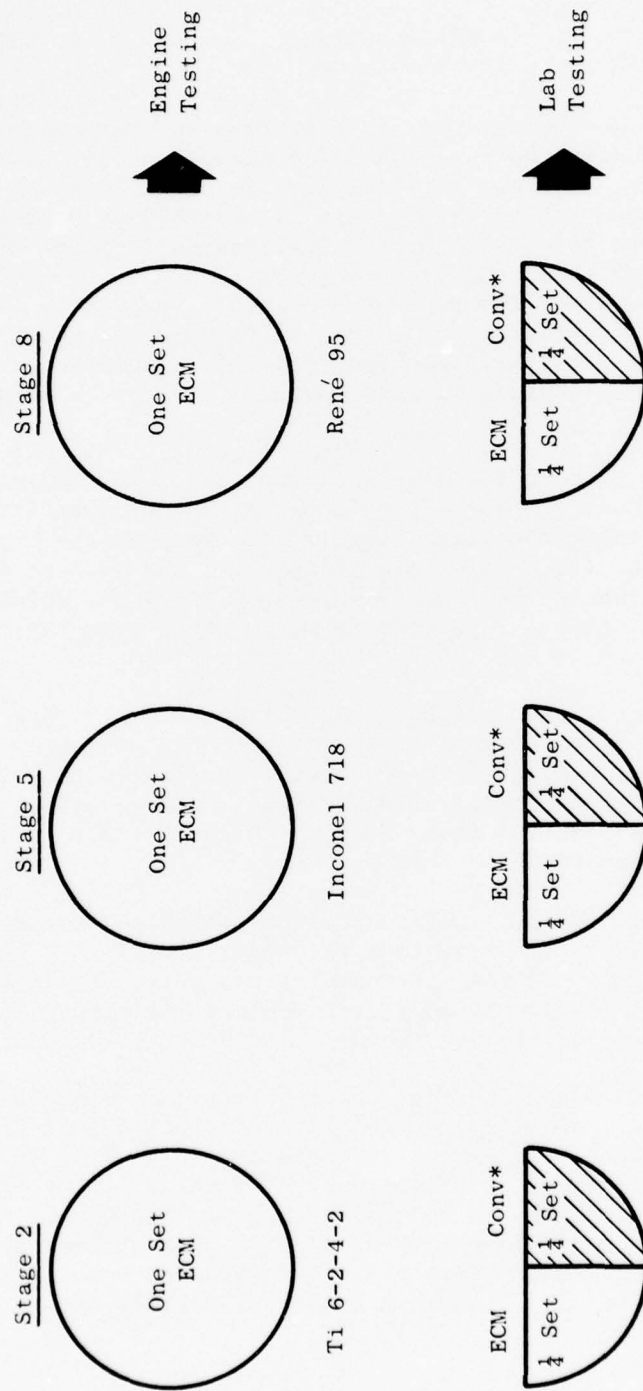

\* Control Sample

Figure 1. ATEGG Option Program.

Work to be accomplished included the following tasks:

- 1) Manufacture by means of electrochemical machining (ECM) of one and a quarter sets of compressor rotor blades for each of three stages of the GE14/J1B3 compressor.
- 2) Manufacture by means of conventional machining one-quarter set of the same stages for use as a control sample.
- 3) Perform a detailed geometry investigation of manufacture results of ECM to assess dimensional consistency.
- 4) Determination of resonant frequency and nodal pattern of each of the three stages of blades (one-quarter set of each machining method).
- 5) Flexural fatigue strength testing of each three stages of blades (one-quarter set of each machining method).
- 6) Determination of the relative cost and delivery of blades made by the two methods.
- 7) Manufacture of about 30 stage-5 blades by machining the dovetail first as would be done in a production process.

Considerable technical difficulty was encountered in the initial production of ECM blades at both the vendors involved in the program which stretched the manufacture of the Stage 2 and 5 blades into mid 1975. Also, difficulty with the powder metal material for the Stage 8 blades was encountered: A lot was scrapped in July of 1974 and the replacement lot delivered in October of 1974 was found to be partly defective. These material problems contributed to a series of delays at the vendor which stretched completion of only a partial set of R95 ECM blades into the last quarter of 1975. A substitute task for the remaining R95 Stage 8 blades was negotiated with the Air Force in the first quarter of 1976 (item 7 in the task list above). The program was completed in April of 1976.

## SECTION II

### SUMMARY


Blades were built using ECM and conventional machining methods. Stages 2, 5, and 8 of the GE14/J1B3 compressor were chosen for this task. They represent different sizes, types of blades, and materials. Stage 2 was made from titanium 6-2-4-2; Stage 5 was made from Inconel 718; and, Stage 8 was made from René 95. These materials present a wide variety of machining difficulty. All materials were originally intended to be cast and wrought (C&W) as is usual practice in airfoil manufacture. In the case of the R95 material for the Stage 8 ECM blades, powder metal (PM) material was used as most representative of a low cost source in keeping with the intent of the study. Both cost and delivery advantages over cast and wrought material were promised for the lot of approximately 100 R95 slugs required for ECM manufacturing when material was ordered early in 1974. Each of the blades generated in this program is shown in Figure 2.

The program proved that blades can be made from a variety of materials and in quantity using a quasi-production-type ECM process for generating the airfoil and adjacent flowpath surfaces. The blades produced by ECM in this program show excellent geometric characteristics relative to blade shape and dimensional consistency. Leading and trailing edge contours can be held well within existing tolerance bonds. Standard deviations on blade chord, maximum thickness, leading edge thickness, and trailing edge thickness are much smaller than standard airfoil tolerances on these variables. Available data on a production blade process indicate that the values shown in a later table for ECM manufacture represent about a 50% improvement in dimensional control over conventional methods.


The ECM vendors were not required to handwork in airfoil and adjacent flowpath surfaces; these surfaces were to be as-machined. Only the vendor for the Stage 5 blades complied with this restriction. Since handwork introduces uncontrolled variability, only the Stage 5 blades are truly representative of the ECM process in a geometric and dynamic sense. For this reason, only the Stage 5 geometry data are included. Section IVA contains the detailed data for reference.

There was found to be no clear cut advantage of ECM's airfoils over airfoils produced by conventional means with regard to natural frequencies and nodal patterns. Stage 5, however, with as-ECM'd surfaces, exhibited consistently better frequency scatter and standard deviation. The variability produced by hand rework on Stages 2 and 8 may have distorted the results.


As-ECM'd blades with peening showed several advantages over conventional blades in areas related to fatigue strength. The standard deviation was found to be smaller than for conventionally made blades. Hence, the average fatigue strength was diminished less for as-ECM'd blades than for conventional blades to obtain the design allowable levels. The fatigue test results are summarized in Table 1, where the 90% confidence column represents

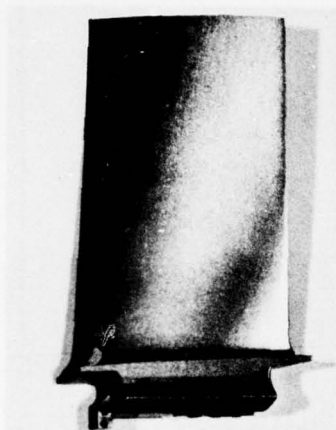


ATEGG OPTION  
STAGE 2  
NONCONVENTIONAL

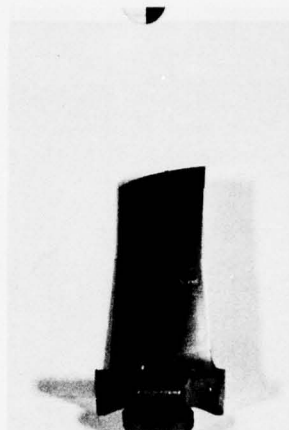


ATEGG OPTION  
STAGE 5  
NONCONVENTIONAL

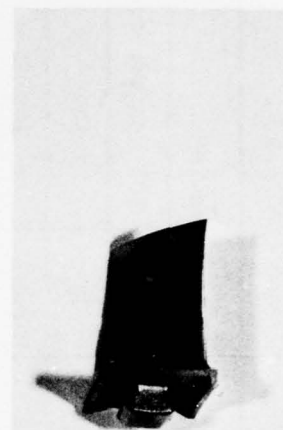


ATEGG OPTION  
STAGE 8  
NONCONVENTIONAL

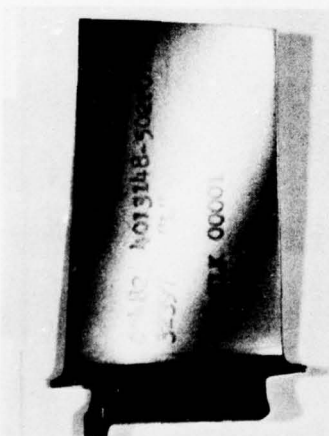

ATEGG OPTION  
STAGE 2  
CONVENTIONAL

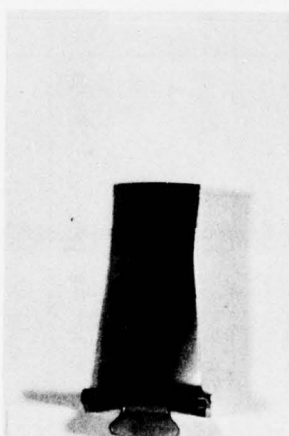

ATEGG OPTION  
STAGE 5  
CONVENTIONAL

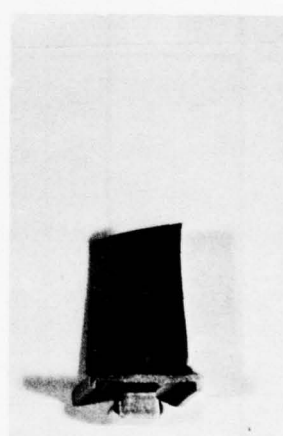

ATEGG OPTION  
STAGE 8  
CONVENTIONAL

Figure 2. GE14 Compressor Blades.

Table 1. Summary of Fatigue Results.

| Configuration        | Material              | Peened ? | Fatigue Strength† |         |                |
|----------------------|-----------------------|----------|-------------------|---------|----------------|
|                      |                       |          | Average           | Std Dev | 90% Confidence |
| Stage 2 (Conv.)      | Ti 6-2-4-2 (C&W)      | Yes      | 141               | 4.3     | 124            |
| Stage 2 (ECM)        | Ti 6-2-4-2 (C&W)      | Yes      | 145               | <1.0    | 143            |
| Stage 5 (Conv.)      | Inconel 718 (C&W)     | Yes      | 142               | 4.1     | 126            |
| Stage 5 (ECM)        | Inconel 718 (C&W)     | No       | 121               | 4.4     | 105            |
| Stage 8 (Conv.)      | René 95 (C&W)         | Yes      | 219               | 4.5     | 202            |
| Stage 8 (ECM)        | René 95 (PM/as-HIP'd) | Yes      | 207               | 3.1     | 195            |
| Stages 7 & 8 (ECM)‡  | René 95 (C&W)         | Yes      | 230               | 1.0     | 226            |
| Stage 5 (ECM)        | René 95 (PM/as-HIP'd) | No       | 131               | 4.3     | 115            |
| Test Specimen (ECM)* | René 95 (C&W)         | No       | 114               | -       | -              |
| Test Specimen (ECM)* | René 95 (C&W)         | Yes      | 210               | -       | -              |
| Test Specimen (ECM)* | René 95 (PM/as-HIP'd) | No       | 124               | -       | -              |
| Test Specimen (ECM)* | René 95 (PM/as-HIP'd) | Yes      | 220               | -       | -              |

† All values are ksida.

‡ Included to correlate PM & C&W from blade tests. Data from a previous Study.

\* Materials data included to correlate effect of peening and C&W and PM.

§ PM is powder metal C&W is cast and wrought.

the useable strength of each blade set. With equivalent material to start, and peening all blades, the ECM process produced blades of higher useable fatigue strength by more than 10%.

A summary of the procurement costs for the program is presented in Table 2. Although these costs are difficult to relate to production cost, it is noteworthy that costs per blade were roughly equivalent, with the relative cost of ECM decreasing with increasing material strength (Stage 8, René 95).

The present program successfully demonstrated ECM manufacture of blades with pre-machined dovetails. This allowed production of a stress-free airfoil with improved fatigue design strength in the peened condition compared to a conventionally produced peened blade. As with the previous ECM blades, dimensional and contour consistency was excellent. This process is believed cost-competitive with conventional processes for current high-strength nickel base alloys and yields high quality blades.

Table 2. Cost Summary

| Stage                                                                                                                                                                                                                                                                                                                                                                                                                                                              | Conv   | ECM                 |
|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|--------|---------------------|
| <u>2</u>                                                                                                                                                                                                                                                                                                                                                                                                                                                           |        |                     |
| Quality                                                                                                                                                                                                                                                                                                                                                                                                                                                            | 15     | 75                  |
| Machining Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                 | 4.3K   | 27.3K               |
| Tooling Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                   | 0      | 3.6K                |
| Cost/Blade, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                     | 268.00 | 306.00              |
| <u>5</u>                                                                                                                                                                                                                                                                                                                                                                                                                                                           |        |                     |
| Quality                                                                                                                                                                                                                                                                                                                                                                                                                                                            | 20     | 102                 |
| Machining Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                 | 6.1K   | 33.7K               |
| Tooling Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                   | 0      | 3.7K                |
| Cost/Blade, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                     | 288.00 | 294.00              |
| <u>5 (R95)</u>                                                                                                                                                                                                                                                                                                                                                                                                                                                     |        |                     |
| Quality                                                                                                                                                                                                                                                                                                                                                                                                                                                            | -      | 30                  |
| Machining Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                 | -      | 16.7K               |
| Tooling Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                   | -      | φ                   |
| Cost/Blade, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                     | **     | 557.90<br>(375.00)* |
| <u>8</u>                                                                                                                                                                                                                                                                                                                                                                                                                                                           |        |                     |
| Quality                                                                                                                                                                                                                                                                                                                                                                                                                                                            | 20     | 100†                |
| Machining Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                 | 7.4K   | 28.9K               |
| Tooling Cost, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                   | 0      | φ                   |
| Cost/Blade, \$                                                                                                                                                                                                                                                                                                                                                                                                                                                     | 248.00 | 289.00              |
| <p>* Based upon a lot size comparable to the other stage lots, the unit cost would reduce to \$375.00. Tooling used was stg 5 Znco 718 tooling.</p> <p>** No conventionally machined R95 stage 5 blades are available for direct comparison.</p> <p>† The program actually produced 58 pieces at this unit price. Further machining was abandoned due to extensive delays in obtaining the PM Rene 95 Material.</p> <p>φ Tooling costs not provided by vendor.</p> |        |                     |

### SECTION III

#### BLADE MANUFACTURE

The nonconventional blades all used ECM to generate the airfoil and adjacent flowpath surfaces; the dovetails were all generated subsequently using EDM. The Stage 5 blade airfoil leading and trailing edges were finished entirely by ECM; those on Stages 2 and 8 were routinely hand polished.

The conventionally machined blades were milled and belt polished to final contour.

The vendors for each of the blades are listed in Table 3.

Table 3. Vendor Listing.

| <u>Stage</u> | <u>Conventional</u> | <u>Unconventional</u> |
|--------------|---------------------|-----------------------|
| 2            | Jarvis              | Metem Corp.           |
| 5            | Jarvis              | Lehr Precision        |
| 8            | Mal                 | Metem Corp.           |

No restrictions were placed on the vendors making the blades by conventional means. The vendors using ECM methods were required to do no hand finishing of airfoil contours -- the flowpath surfaces were to be completely generated by the ECM process. The vendors doing the ECM blades were permitted to generate the dovetail form by use of electrodischarge machining (EDM).

The material used for Stages 2 and 5 was cast and wrought. This was originally the plan for Stage 8 also. However, it was identified part-way through the program that as-HIP'd power metal (PM) René 95 material could be obtained for this stage. The decision was made to go with PM since it represents an additional cost advantage, primarily for ECM blades. When the decision was made to go with PM, it was too late to stop the conventional machining vendor from using cast and wrought material; however, the ECM vendor was redirected to using PM. As will be noted later, this necessitated additional bench testing.

Only the vendor doing the Stage 5 blades by ECM complied with the restriction of no handwork on airfoil surfaces. Handworking produces surface stresses that can significantly affect the base fatigue of a part. Therefore, the ECM Stages 2 and 8 blades (which were both made by the same vendor) had to be glass-bead peened.

A cost summary is shown in Table 2 as it relates to the limited blade procurement for this program. There is difficulty in generating representative data for production quantities for the ECM blades; whereas, the conventional approach (closed die forging or roll forming) has a well-documented cost history. Current equipment limitations in the ECM area, in the field of solid state electronic process parameter controllers, make predictions very subjective. However, our experience on this program allows us to make a very optimistic forecast that blade costs for materials such as René 95 and Inconel 718 will be comparable to those for titanium blades produced conventionally.

The data presented in the subsequent sections illustrate that ECM'd blades are technically equivalent or superior to conventionally made blades. However, the question of economics must be addressed. With current technology, there is no advantage to generating titanium blades by ECM. Conventional methods of forging to size and/or roll forming are clearly superior. Scrap rates are low and die life is high because of relatively easy forming characteristics of titanium alloys. Existing press capacity size is likewise no problem.

The introduction of nickel-base blade materials, especially René 95, swings the balance in favor of ECM. In the case of Inconel 718, there is a slight advantage to ECM; and, in the case of René 95, the scales are tipped completely to ECM's favor. These are necessarily subjective evaluations that should be substantiated by thorough economic analysis.

Many areas of manufacture by ECM require development. Foremost of these is full utilization of solid state low voltage controls for power supplied. This would permit considerable improvement in filtering out noise "dirty extraneous electrics" that confuse present spark detection devices. This feature is critical to process cost control to assure protection of expensively shaped cathodes.

At present, cathode design for the ECM is a process trial and error procedure. However, with full control of all variable process parameters, design of the cathodes becomes predictable. Translation of an airfoil shape to a cathode could then be achieved by numerically controlled machining of this shape much the same as airfoils are now conventionally machined.

No attempt was made during the initial phase of the ECM study to optimize the manufacturing sequence to be cost effective. The program concentrated on the production of a high quality airfoil and, therefore, machined the dovetail last because of concern that the completed dovetail would be damaged when it carried the high current involved in the ECM generation of the airfoil. At the end of this phase of work it was apparent that the processing sequence needed to be changed to make ECM airfoils manufacture cost competitive for high temperature materials. Of the items requiring improvement, only the need to complete all machining of the dovetail and platform underside prior to generation of the airfoil to free the airfoil of fatigue stresses induced while holding the airfoil to machine the dovetail

in the original process was believed a significant difficulty for production manufacturing. The specific problem was the limited shank size available. Further, problems of reliably sealing a charged electrode during the ECM process from the shank area were believed to provide a further barrier. As a result of these questions in the cost effective process, the present program was proposed and accepted by the Air Force to offset the 42 blade short fall in the Stage 8 R95 manufacture.

Construction of a 4 blade pilot lot of Stage 5 airfoils was completed using an ECM process, R95 PM material and with premachined dovetails. With the success of the pilot lot, work was begun to produce the remaining 26 required airfoils.

The work of producing the lot of 30 airfoils was done at Lehr Precision, the vendor where the Stage 5 blades were made by ECM from Inconel 718 material during the original phase of the program. After several approaches were studied for the dovetail first manufacture process, a metal matrix was cast around the finished dovetail to provide a piece for the ECM process which directly resembled the blank before the dovetail was machined. This arrangement isolated the dovetail from the charged electrolyte and provided a sufficient cross section for the high current of the ECM blade processing. The arrangement also provided reliable fixturing surfaces for both the ECM process and the subsequent grinding operations (needed to finish the four sides of the blade platform).

## SECTION IV

### TESTING AND INSPECTION

#### A. Dimensional Checks

The Stage 5 ECM'd blades were inspected thoroughly, piece by piece, using inspection gaging built for this specific purpose. Inspection Sections B-B, C-C, D-D, E-E, F-F, G-G, and H-H were used to obtain measurements of airfoil chord, leading edge thickness, maximum thickness, and trailing edge thicknesses. Of interest here was the variation obtained from blade to blade. The blade sections are defined on Figure 3. The measured geometric data for the Stage 5 blade is summarized in Table 4. Included for reference is the tolerance given for production blades made by conventional methods. No measurements were made on the control sets of blades in this study or on the Stages 2 and 8 ECM'd blades, because it was believed that the hand finishing involved resulted in larger tolerances than the production tolerances quoted as a reference.

The detailed part-by-part tabulation of measurement results is presented in Table 5, for the original 120 piece lot of Inco 718 ECM blades.

The R95 Stage 5 ECM blades were inspected at Stations B-B, D-D and F-F and the values of chord, leading edge thickness, maximum thickness and trailing edge thickness were determined. A summary of these variations is included in Table 5. Note that all dimensions are as manufactured, without any hand finishing. Again, airfoil contours and edges were excellent. Leading and trailing edge contours were particularly smooth and consistent.


#### B. Frequencies and Nodal Patterns

One quarter set of each stage and type of manufacture was tested for resonant frequencies and nodal patterns. To accomplish this, the blades were clamped in a fixture simulating the root fixity that exists in an engine and were excited by a variable frequency electromagnetic drive at the individual blade's natural frequencies. Figure 4 represents a typical test setup with a much larger blade than dealt with here. Nodal patterns were traced out manually on the part using a crystal pickup. The nodal patterns then were transferred by scaling them on full-size drawings.

The measured frequencies are presented in Tables 6 through 11 for the ECM and conventional blades of Stages 2, 5, and 8, respectively. Frequencies up to 20,000 Hz are included.

The resulting frequencies and spread in frequencies are presented in Figures 5, 6, and 7 for Stages 2, 5, and 8, respectively.

As an example, the nodal patterns for the Stage 2 ECM blades are provided in Figures 8 through 11.

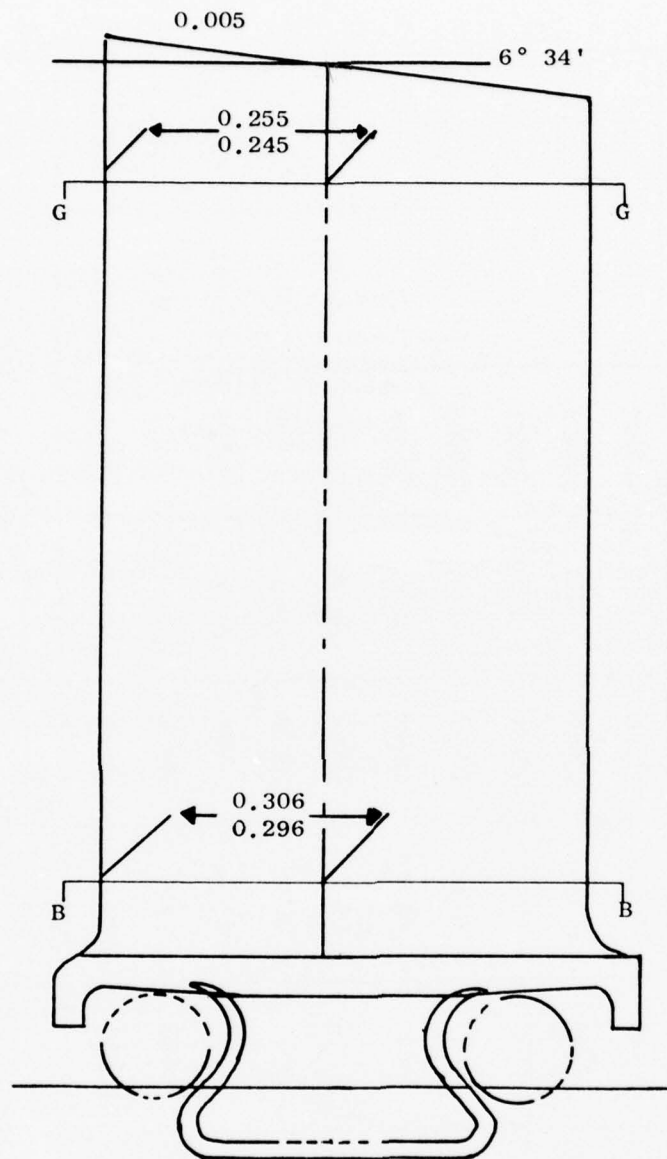

| Section | Chord<br>Overall<br>±0.007 | Maximum<br>+0.005<br>-0.002 | Thickness<br>Leading<br>+0.003<br>-0.002 | Trailing<br>+0.005<br>-0.002 |
|---------|----------------------------|-----------------------------|------------------------------------------|------------------------------|
| A-A     | 0.871                      | 0.075                       | 0.021                                    | 0.024                        |
| B-B     | ± 0.869                    | ± 0.074                     | ± 0.023                                  | ± 0.023                      |
| C-C     | 0.860                      | 0.072                       | 0.022                                    | 0.022                        |
| D-D     | ± 0.852                    | ± 0.064                     | ± 0.021                                  | ± 0.021                      |
| E-E     | 0.844                      | 0.050                       | 0.081                                    | 0.081                        |
| F-F     | ± 0.835                    | ± 0.038                     | ± 0.016                                  | ± 0.016                      |
| G-G     | 0.827                      | 0.034                       | 0.014                                    | 0.014                        |
| H-H     | 0.819                      | 0.033                       | 0.013                                    | 0.013                        |

Figure 3. Stage 5 Geometry.

Table 4. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01.

| Section                   | Chord          |         | Maximum Thickness |         | LE Thickness   |         | TE Thickness   |         |
|---------------------------|----------------|---------|-------------------|---------|----------------|---------|----------------|---------|
|                           | Mean           | Std Dev | Mean              | Std Dev | Mean           | Std Dev | Mean           | Std Dev |
| B-B                       | -.0044         | .0020   | -.0011            | .0008   | -.0027         | .0010   | -.0022         | .0012   |
| C-C                       | -.0048         | .0018   | -.0026            | .0008   | -.0015         | .0007   | -.0012         | .0011   |
| D-D                       | .0037          | .0017   | -.0017            | .0006   | -.0013         | .0007   | .0000          | .0001   |
| E-E                       | .0025          | .0017   | .0005             | .0006   | -.0012         | .0005   | -.0005         | .0009   |
| F-F                       | .0024          | .0017   | -.0008            | .0006   | .0001          | .0006   | -.0023         | .0009   |
| G-G                       | .0037          | .0038   | -.0020            | .0006   | -.0006         | .0007   | .0005          | .0009   |
| H-H                       | .0051          | .0067   | -.0009            | .0008   | .0010          | .0005   | .0003          | .0003   |
| B-B*                      | -.0009         | .0029   | +.0023            | .0008   | +.0024         | .0010   | +.0003         | .0013   |
| D-D*                      | +.0007         | .0035   | +.0014            | .0009   | +.0024         | .0012   | +.0016         | .0011   |
| F-F*                      | +.0027         | .0033   | +.0028            | .0010   | +.0025         | .0011   | +.0017         | .0011   |
| Drawing Tolerance         | +.007<br>-.007 |         | +.005<br>-.002    |         | +.005<br>-.002 |         | +.005<br>-.002 |         |
| * 26 Blade Sample, PM R95 |                |         |                   |         |                |         |                |         |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01.

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |        |        |        |        |        |        |        |        |        |
|---------|------------|---------------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
|         |            |                     | 22            | 23     | 24     | 25     | 26     | 27     | 28     | 29     | 30     | 31     |
| B-B     | CHORD      | +.007               | -.0035        | -.0010 | -.0015 | -.0015 | +.0010 | -.0030 | +.0000 | -.0015 | +.0000 | +.0000 |
|         |            | -.007               |               |        |        |        |        |        |        |        |        |        |
|         | MAX THK    | +.005               | +.0010        | +.0005 | +.0005 | +.0010 | +.0000 | +.0000 | +.0000 | +.0000 | +.0000 | +.0005 |
|         |            | -.002               |               |        |        |        |        |        |        |        |        |        |
| C-C     | LE THK     | +.005               | -.0010        | -.0010 | -.0010 | -.0020 | -.0010 | -.0020 | -.0010 | -.0020 | -.0015 | -.0015 |
|         |            | -.002               |               |        |        |        |        |        |        |        |        |        |
|         | TE THK     | +.005               | +.0005        | +.0005 | +.0005 | +.0015 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0010 |
|         |            | -.002               |               |        |        |        |        |        |        |        |        |        |
| D-D     | CHORD      |                     | +.0040        | +.0050 | +.0050 | +.0050 | +.0065 | +.0040 | +.0060 | +.0055 | +.0065 | +.0075 |
|         | MAX THK    |                     | +.0000        | -.0005 | -.0005 | -.0010 | +.0000 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 |
|         | LE THK     |                     | +.0000        | -.0005 | +.0000 | -.0005 | +.0000 | -.0010 | -.0005 | -.0010 | -.0005 | -.0005 |
|         | TE THK     |                     | +.0020        | +.0020 | +.0020 | +.0020 | +.0030 | +.0020 | +.0020 | +.0020 | +.0025 | +.0030 |
| E-E     | CHORD      |                     | +.0025        | +.0025 | +.0030 | +.0040 | +.0050 | +.0020 | +.0045 | +.0040 | +.0050 | +.0055 |
|         | MAX THK    |                     | +.0020        | +.0020 | +.0010 | +.0010 | +.0025 | +.0010 | +.0015 | +.0015 | +.0010 | +.0015 |
|         | LE THK     |                     | +.0000        | -.0010 | -.0005 | -.0010 | +.0000 | -.0010 | -.0005 | -.0010 | -.0010 | -.0010 |
|         | TE THK     |                     | +.0020        | +.0015 | +.0015 | +.0010 | +.0020 | +.0010 | +.0020 | +.0010 | +.0015 | +.0020 |
| F-F     | CHORD      |                     | +.0030        | +.0025 | +.0035 | +.0045 | +.0055 | +.0030 | +.0040 | +.0045 | +.0060 | +.0060 |
|         | MAX THK    |                     | +.0000        | +.0000 | +.0000 | +.0000 | +.0005 | +.0000 | -.0005 | +.0000 | +.0000 | +.0005 |
|         | LE THK     |                     | +.0010        | +.0000 | +.0005 | +.0000 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 | +.0005 |
|         | TE THK     |                     | +.0000        | -.0005 | -.0010 | -.0010 | -.0005 | -.0015 | -.0010 | -.0015 | -.0005 | -.0010 |
| G-G     | CHORD      |                     | +.0030        | +.0020 | +.0030 | +.0035 | +.0040 | +.0020 | +.0035 | +.0040 | +.0050 | +.0060 |
|         | MAX THK    |                     | -.0010        | -.0015 | -.0010 | -.0010 | -.0005 | -.0015 | -.0010 | -.0010 | -.0010 | -.0010 |
|         | LE THK     |                     | +.0000        | -.0010 | +.0000 | -.0005 | +.0000 | -.0010 | +.0000 | -.0010 | -.0010 | +.0000 |
|         | TE THK     |                     | +.0020        | +.0020 | +.0020 | +.0020 | +.0030 | +.0010 | +.0000 | +.0020 | +.0020 | +.0025 |
| H-H     | CHORD      |                     | +.0045        | +.0020 | +.0035 | +.0040 | +.0045 | +.0030 | +.0045 | +.0050 | +.0060 | +.0075 |
|         | MAX THK    |                     | -.0010        | -.0015 | -.0015 | -.0015 | -.0020 | -.0015 | -.0015 | -.0015 | -.0015 | -.0010 |
|         | LE THK     |                     | +.0015        | +.0000 | +.0005 | +.0000 | +.0000 | +.0010 | +.0020 | +.0005 | +.0000 | +.0000 |
|         | TE THK     |                     | +.0020        | +.0010 | +.0010 | +.0010 | +.0015 | +.0010 | +.0015 | +.0015 | +.0015 | +.0020 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOLE-RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|------------|------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                  | 32            | 33      | 34      | 35      | 36      | 37      | 38      | 39      | 40      | 41      |
| B-B     | CHORD      | + .007           | - .0025       | - .0030 | - .0120 | - .0090 | - .0020 | - .0040 | - .0060 | - .0045 | - .0040 | - .0040 |
|         |            | - .007           |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005           | + .0000       | + .0000 | - .0020 | - .0020 | - .0010 | - .0005 | - .0005 | - .0005 | - .0010 | - .0010 |
| C-C     |            | - .002           |               |         |         |         |         |         |         |         |         |         |
|         | LE THK     | + .005           | - .0020       | - .0025 | - .0045 | - .0040 | - .0025 | - .0020 | - .0015 | - .0020 | - .0020 | - .0020 |
|         |            | - .002           |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005           | + .0000       | - .0010 | - .0030 | - .0030 | - .0015 | - .0020 | - .0020 | - .0030 | - .0020 | - .0020 |
|         |            | - .002           |               |         |         |         |         |         |         |         |         |         |
| D-D     | CHORD      | + .005           | + .0010       | + .0000 | - .0080 | - .0040 | - .0010 | - .0005 | - .0010 | + .0000 | - .0010 | - .0050 |
|         | MAX THK    | - .0015          | - .0015       | - .0015 | - .0040 | - .0035 | - .0020 | - .0020 | - .0020 | - .0020 | - .0025 | - .0025 |
|         | LE THK     | - .0010          | - .0010       | - .0010 | - .0040 | - .0030 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 |
|         | TE THK     | + .0005          | + .0000       | - .0020 | - .0020 | - .0020 | - .0005 | + .0000 | + .0000 | - .0005 | - .0005 | - .0005 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |
| E-E     | CHORD      | + .0050          | + .0050       | + .0040 | - .0040 | - .0005 | + .0030 | + .0040 | + .0030 | + .0035 | + .0030 | + .0035 |
|         | MAX THK    | - .0010          | - .0010       | - .0015 | - .0035 | - .0035 | - .0020 | - .0020 | - .0020 | - .0020 | - .0020 | - .0020 |
|         | LE THK     | - .0010          | - .0010       | - .0015 | - .0040 | - .0030 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 |
|         | TE THK     | + .0020          | + .0010       | - .0010 | - .0010 | - .0010 | + .0005 | + .0010 | + .0010 | + .0000 | + .0005 | + .0010 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |
| F-F     | CHORD      | + .0035          | + .0020       | - .0020 | - .0065 | - .0030 | + .0015 | + .0025 | + .0015 | + .0015 | + .0015 | + .0020 |
|         | MAX THK    | + .0015          | + .0010       | - .0010 | - .0010 | - .0015 | + .0005 | + .0005 | + .0005 | + .0005 | + .0005 | + .0010 |
|         | LE THK     | - .0010          | - .0015       | - .0040 | - .0040 | - .0030 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 |
|         | TE THK     | + .0015          | + .0005       | - .0010 | - .0010 | - .0020 | - .0010 | + .0000 | - .0005 | - .0010 | - .0005 | + .0000 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |
| G-G     | CHORD      | + .0040          | + .0025       | - .0080 | - .0030 | - .0030 | + .0010 | + .0025 | + .0020 | + .0020 | + .0020 | + .0020 |
|         | MAX THK    | + .0000          | - .0005       | - .0035 | - .0030 | - .0030 | - .0020 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 |
|         | LE THK     | + .0000          | + .0000       | - .0035 | + .0000 | + .0000 | + .0015 | + .0000 | + .0000 | + .0000 | + .0000 | + .0005 |
|         | TE THK     | - .0015          | - .0015       | - .0040 | - .0040 | - .0040 | - .0025 | - .0020 | - .0020 | - .0025 | - .0025 | - .0020 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |
| H-H     | CHORD      | + .0035          | + .0025       | - .0100 | - .0045 | - .0045 | + .0010 | + .0025 | + .0020 | + .0015 | + .0025 | + .0020 |
|         | MAX THK    | - .0010          | - .0015       | - .0055 | - .0040 | - .0040 | - .0030 | - .0020 | - .0020 | - .0020 | - .0020 | - .0020 |
|         | LE THK     | - .0010          | - .0010       | - .0055 | - .0030 | - .0030 | - .0020 | - .0010 | - .0005 | - .0010 | - .0005 | + .0000 |
|         | TE THK     | + .0030          | + .0015       | - .0010 | - .0010 | - .0010 | + .0015 | - .0020 | + .0020 | + .0015 | + .0015 | + .0020 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |
|         | CHORD      | + .0050          | + .0035       | - .0140 | + .0000 | + .0000 | + .0020 | + .0040 | + .0035 | + .0030 | + .0040 | + .0035 |
|         | MAX THK    | - .0015          | - .0020       | - .0060 | - .0045 | - .0045 | - .0045 | - .0025 | - .0020 | - .0020 | - .0020 | - .0020 |
|         | LE THK     | + .0000          | - .0005       | + .0000 | - .0010 | - .0010 | - .0010 | - .0005 | - .0010 | - .0005 | + .0010 | + .0010 |
|         | TE THK     | + .0015          | + .0010       | - .0020 | + .0000 | + .0000 | + .0000 | + .0005 | + .0010 | + .0005 | + .0000 | + .0000 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |         |
|---------|------------|---------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                     | 42            | 43      | 44      | 45      | 46      | 47      | 48      | 49      | 50      | 51      |         |
| B-B     | CHORD      | + .007<br>-.007     | -.0060        | -.0050  | -.0060  | -.0050  | --      | -.0020  | -.0020  | -.0030  | -.0030  | -.0030  | -.0030  |
|         | MAX THK    | + .005<br>-.002     | -.0015        | -.0010  | -.0015  | --      | + .0000 | -.0005  | -.0005  | -.0010  | -.0010  | -.0010  | -.0010  |
|         | LE THK     | + .005<br>-.002     | -.0030        | -.0025  | -.0025  | --      | -.0010  | -.0015  | -.0015  | -.0015  | -.0015  | -.0020  | -.0020  |
|         | TE THK     | + .005<br>-.002     | -.0030        | -.0020  | -.0025  | --      | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0020  | -.0020  |
| C-C     | CHORD      |                     | -.0015        | + .0000 | -.0020  | -.0010  | --      | + .0020 | + .0015 | + .0020 | + .0005 | + .0005 | + .0005 |
|         | MAX THK    |                     | -.0030        | -.0015  | -.0025  | -.0025  | --      | -.0015  | -.0015  | -.0020  | -.0030  | -.0020  | -.0020  |
|         | LE THK     |                     | -.0005        | -.0015  | -.0015  | -.0015  | --      | -.0000  | -.0005  | -.0005  | -.0010  | -.0010  | -.0010  |
|         | TE THK     |                     | -.0010        | + .0000 | -.0010  | -.0010  | --      | -.0005  | -.0005  | -.0005  | -.0010  | -.0010  | -.0010  |
| D-D     | CHORD      |                     | + .0020       | + .0035 | + .0015 | + .0025 | --      | + .0050 | + .0050 | + .0050 | + .0035 | + .0040 | + .0040 |
|         | MAX THK    |                     | -.0025        | -.0020  | -.0020  | -.0025  | --      | -.0010  | -.0015  | -.0015  | -.0020  | -.0020  | -.0020  |
|         | LE THK     |                     | -.0015        | -.0010  | -.0010  | -.0015  | --      | + .0000 | -.0005  | -.0005  | -.0005  | -.0010  | -.0010  |
|         | TE THK     |                     | + .0000       | + .0000 | + .0000 | + .0005 | --      | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0005 |
| E-E     | CHORD      |                     | + .0005       | + .0020 | + .0000 | + .0010 | --      | + .0040 | + .0035 | + .0035 | + .0020 | + .0025 | + .0025 |
|         | MAX THK    |                     | -.0005        | + .0005 | + .0000 | + .0005 | --      | + .0005 | + .0010 | + .0010 | + .0005 | + .0005 | + .0005 |
|         | LE THK     |                     | -.0015        | -.0010  | -.0010  | -.0010  | --      | + .0000 | -.0005  | -.0010  | -.0010  | -.0010  | -.0010  |
|         | TE THK     |                     | -.0010        | + .0000 | -.0010  | -.0005  | --      | + .0000 | + .0000 | + .0000 | -.0005  | -.0005  | -.0005  |
| F-F     | CHORD      |                     | + .0005       | + .0020 | + .0005 | + .0015 | --      | + .0040 | + .0040 | + .0040 | + .0035 | + .0030 | + .0030 |
|         | MAX THK    |                     | -.0015        | -.0010  | -.0020  | -.0010  | --      | -.0005  | -.0005  | -.0015  | -.0015  | -.0010  | -.0010  |
|         | LE THK     |                     | -.0005        | + .0000 | + .0000 | + .0000 | --      | + .0010 | + .0010 | + .0005 | + .0005 | + .0005 | + .0005 |
|         | TE THK     |                     | -.0030        | -.0025  | -.0025  | -.0020  | --      | -.0020  | -.0010  | -.0020  | -.0020  | -.0020  | -.0020  |
| G-G     | CHORD      |                     | + .0010       | + .0015 | + .0000 | + .0020 | --      | + .0040 | + .0040 | + .0040 | + .0030 | + .0025 | + .0025 |
|         | MAX THK    |                     | -.0025        | -.0020  | -.0020  | -.0020  | --      | -.0015  | -.0020  | -.0025  | -.0025  | -.0020  | -.0020  |
|         | LE THK     |                     | -.0010        | -.0010  | -.0010  | -.0010  | --      | + .0000 | -.0005  | -.0010  | -.0005  | -.0005  | -.0005  |
|         | TE THK     |                     | + .0010       | + .0015 | + .0015 | + .0015 | --      | + .0010 | + .0020 | + .0015 | + .0010 | + .0015 | + .0015 |
| H-H     | CHORD      |                     | + .0025       | + .0030 | + .0025 | + .0040 | --      | + .0070 | + .0060 | + .0055 | + .0050 | + .0050 | + .0050 |
|         | MAX THK    |                     | -.0025        | -.0020  | -.0025  | -.0020  | --      | -.0020  | -.0020  | -.0015  | -.0015  | -.0020  | -.0020  |
|         | LE THK     |                     | + .0000       | + .0005 | + .0005 | + .0005 | --      | + .0015 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 |
|         | TE THK     |                     | + .0000       | + .0000 | + .0000 | + .0000 | --      | + .0005 | + .0005 | + .0005 | + .0000 | + .0000 | + .0000 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|------------|---------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                     | 52            | 53      | 54      | 55      | 56      | 57      | 58      | 59      | 60      | 61      |
| B-B     | CHORD      | + .007              | -.0005        | -.0030  | -.0015  | -.0025  | -.0020  | -.0035  | -.0010  | -.0020  | -.0025  | -.0030  |
|         |            | - .007              |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005              | -.0005        | -.0005  | -.0010  | + .0005 | + .0000 | -.0005  | -.0005  | + .0000 | -.0005  | -.0010  |
|         |            | - .002              |               |         |         |         |         |         |         |         |         |         |
|         | LE THK     | + .005              | -.0020        | -.0020  | -.0015  | -.0020  | -.0015  | -.0010  | -.0010  | -.0010  | -.0015  | -.0015  |
|         |            | - .002              |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005              | -.0020        | -.0020  | -.0010  | -.0020  | -.0010  | -.0010  | -.0005  | -.0005  | -.0010  | -.0010  |
|         |            | - .002              |               |         |         |         |         |         |         |         |         |         |
| C-C     | CHORD      |                     | -.0005        | + .0010 | + .0015 | + .0010 | + .0020 | -.0010  | + .0020 | + .0010 | + .0015 | + .0010 |
|         | MAX THK    |                     | -.0020        | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0015  | -.0015  | -.0020  | -.0020  |
|         | LE THK     |                     | -.0010        | -.0010  | -.0010  | -.0010  | -.0005  | + .0000 | + .0000 | + .0000 | -.0005  | -.0005  |
|         | TE THK     |                     | + .0000       | + .0000 | -.0005  | + .0000 | + .0000 | + .0010 | -.0005  | -.0005  | + .0000 | -.0010  |
| D-D     | CHORD      |                     | + .0030       | + .0050 | + .0050 | + .0050 | + .0060 | + .0030 | + .0060 | + .0050 | + .0050 | + .0040 |
|         | MAX THK    |                     | -.0015        | -.0020  | -.0020  | -.0020  | -.0015  | -.0010  | -.0015  | -.0010  | -.0015  | -.0020  |
|         | LE THK     |                     | -.0005        | -.0005  | -.0005  | -.0005  | -.0005  | + .0000 | + .0000 | + .0000 | -.0010  | -.0010  |
|         | TE THK     |                     | + .0010       | + .0010 | + .0010 | + .0010 | + .0005 | + .0010 | + .0020 | + .0010 | + .0010 | + .0005 |
| E-E     | CHORD      |                     | + .0020       | + .0040 | + .0040 | + .0035 | + .0050 | + .0005 | + .0050 | + .0030 | + .0030 | + .0025 |
|         | MAX THK    |                     | + .0005       | + .0005 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0015 | + .0010 | + .0005 |
|         | LE THK     |                     | -.0010        | -.0010  | -.0010  | -.0010  | -.0005  | -.0005  | -.0005  | + .0000 | -.0010  | -.0010  |
|         | TE THK     |                     | -.0005        | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0010 | + .0000 | + .0000 | + .0000 |
| F-F     | CHORD      |                     | + .0020       | + .0040 | + .0040 | + .0040 | + .0050 | + .0000 | + .0050 | + .0035 | + .0030 | + .0020 |
|         | MAX THK    |                     | -.0010        | -.0005  | -.0010  | -.0010  | -.0005  | -.0010  | -.0005  | -.0005  | -.0005  | -.0010  |
|         | LE THK     |                     | + .0005       | + .0005 | + .0005 | + .0005 | + .0000 | + .0000 | + .0005 | + .0010 | + .0010 | + .0005 |
|         | TE THK     |                     | -.0020        | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0015  | -.0020  | -.0020  | -.0020  |
| G-G     | CHORD      |                     | + .0020       | + .0030 | + .0040 | + .0035 | + .0045 | + .0010 | + .0050 | + .0050 | + .0035 | + .0020 |
|         | MAX THK    |                     | -.0020        | -.0020  | -.0015  | -.0020  | -.0015  | -.0020  | -.0015  | -.0015  | -.0015  | -.0020  |
|         | LE THK     |                     | -.0005        | + .0000 | + .0000 | -.0005  | + .0000 | -.0010  | + .0010 | + .0005 | + .0000 | -.0005  |
|         | TE THK     |                     | + .0020       | + .0015 | + .0020 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0005 |
| H-H     | CHORD      |                     | + .0045       | + .0050 | + .0055 | + .0055 | + .0060 | + .0035 | + .0060 | + .0060 | + .0045 | + .0030 |
|         | MAX THK    |                     | -.0015        | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0015  | -.0015  | -.0015  | -.0020  |
|         | LE THK     |                     | + .0010       | + .0010 | + .0010 | + .0015 | + .0015 | + .0015 | + .0015 | + .0010 | + .0010 | + .0005 |
|         | TE THK     |                     | + .0010       | + .0005 | + .0005 | + .0005 | + .0005 | + .0005 | + .0000 | + .0000 | + .0000 | + .0000 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-RANCE | SERIAL NUMBER |    |         |         |         |         |         |         |         |         |
|---------|------------|-----------------|---------------|----|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                 | 62            | 63 | 64      | 65      | 66      | 67      | 68      | 69      | 70      | 71      |
| B-B     | CHORD      | + .007          | -.0020        | -- | -.0050  | -.0040  | -.0050  | -.0045  | -.0070  | -.0050  | -.0035  | -.0050  |
|         |            | -.007           |               |    |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005          | -.0015        | -- | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  |
|         |            | -.002           |               |    |         |         |         |         |         |         |         |         |
|         | LE THK     | + .005          | -.0015        | -- | -.0020  | -.0025  | -.0025  | -.0025  | -.0020  | -.0025  | -.0030  | -.0030  |
|         |            | -.002           |               |    |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005          | -.0010        | -- | -.0025  | -.0020  | -.0020  | -.0020  | -.0020  | -.0010  | -.0020  | -.0025  |
|         |            | -.002           |               |    |         |         |         |         |         |         |         |         |
| C-C     | CHORD      |                 | + .0005       | -- | + .0005 | + .0000 | + .0005 | + .0000 | -.0050  | + .0000 | -.0005  | -.0050  |
|         | MAX THK    |                 | -.0025        | -- | -.0025  | -.0025  | -.0030  | -.0025  | -.0025  | -.0025  | -.0025  | -.0030  |
|         | LE THK     |                 | -.0010        | -- | -.0010  | -.0010  | -.0015  | -.0010  | -.0015  | -.0010  | -.0015  | -.0020  |
|         | TE THK     |                 | -.0010        | -- | -.0020  | -.0015  | -.0015  | -.0015  | -.0010  | -.0010  | -.0015  | -.0010  |
| D-D     | CHORD      |                 | + .0040       | -- | + .0050 | + .0050 | + .0045 | + .0045 | -.0050  | + .0040 | + .0035 | + .0035 |
|         | MAX THK    |                 | -.0020        | -- | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0020  | -.0015  |
|         | LE THK     |                 | -.0010        | -- | -.0010  | -.0010  | -.0010  | -.0010  | -.0005  | -.0010  | -.0010  | -.0005  |
|         | TE THK     |                 | + .0000       | -- | + .0000 | + .0000 | + .0000 | + .0000 | + .0005 | + .0005 | + .0000 | + .0000 |
| E-E     | CHORD      |                 | + .0025       | -- | + .0030 | + .0030 | + .0030 | + .0030 | -.0015  | + .0030 | + .0025 | + .0025 |
|         | MAX THK    |                 | + .0005       | -- | + .0005 | + .0010 | + .0015 | + .0010 | + .0005 | + .0005 | + .0010 | + .0005 |
|         | LE THK     |                 | -.0010        | -- | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  |
|         | TE THK     |                 | -.0010        | -- | -.0010  | +.0000  | -.0010  | + .0000 | + .0000 | + .0000 | -.0010  | -.0005  |
| F-F     | CHORD      |                 | + .0020       | -- | + .0030 | + .0030 | + .0025 | + .0030 | -.0025  | + .0025 | + .0020 | + .0020 |
|         | MAX THK    |                 | -.0010        | -- | -.0010  | -.0005  | -.0010  | -.0005  | -.0010  | -.0005  | -.0005  | -.0010  |
|         | LE THK     |                 | + .0005       | -- | + .0010 | + .0010 | + .0010 | + .0010 | + .0000 | + .0005 | + .0005 | + .0005 |
|         | TE THK     |                 | -.0025        | -- | -.0025  | -.0020  | -.0025  | -.0020  | -.0020  | -.0020  | -.0025  | -.0025  |
| G-G     | CHORD      |                 | + .0030       | -- | + .0040 | + .0040 | + .0030 | + .0035 | -.0025  | + .0040 | + .0030 | + .0030 |
|         | MAX THK    |                 | -.0020        | -- | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  |
|         | LE THK     |                 | -.0005        | -- | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 |
|         | TE THK     |                 | + .0005       | -- | + .0000 | + .0005 | + .0000 | + .0000 | + .0000 | + .0005 | + .0000 | + .0000 |
| H-H     | CHORD      |                 | + .0040       | -- | + .0060 | + .0065 | + .0065 | + .0060 | + .0010 | + .0070 | + .0060 | + .0060 |
|         | MAX THK    |                 | -.0010        | -- | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  |
|         | LE THK     |                 | + .0005       | -- | + .0010 | + .0015 | + .0015 | + .0010 | + .0015 | + .0015 | + .0015 | + .0015 |
|         | TE THK     |                 | + .0000       | -- | + .0000 | + .0005 | + .0000 | + .0005 | + .0000 | + .0010 | + .0000 | + .0005 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS.<br>TYPE | DRNG.<br>TOLE-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|---------------|-------------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |               |                         | 72            | 73      | 74      | 75      | 76      | 77      | 78      | 79      | 80      | 81      |
| B-B     | CHORD         | + .007                  | -.0050        | -.0050  | -.0045  | -.0030  | -.0030  | -.0040  | -.0050  | -.0040  | -.0040  | -.0030  |
|         |               | -.007                   |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK       | + .005                  | -.0020        | -.0015  | -.0010  | -.0015  | -.0010  | -.0015  | -.0015  | -.0015  | -.0015  | -.0010  |
|         |               | -.002                   |               |         |         |         |         |         |         |         |         |         |
|         | LE THK        | + .005                  | -.0030        | -.0030  | -.0025  | -.0025  | -.0020  | -.0025  | -.0030  | -.0035  | -.0025  | -.0025  |
|         |               | -.002                   |               |         |         |         |         |         |         |         |         |         |
|         | TE THK        | + .005                  | -.0020        | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0030  | -.0020  | -.0020  | -.0020  |
|         |               | -.002                   |               |         |         |         |         |         |         |         |         |         |
| C-C     | CHORD         | -.0005                  | -.0005        | -.0010  | + .0000 | -.0015  | + .0020 | + .0005 | -.0010  | -.0005  | -.0005  | + .0005 |
|         | MAX THK       | -.0030                  | -.0030        | -.0025  | -.0025  | -.0030  | -.0025  | -.0030  | -.0030  | -.0030  | -.0025  | -.0025  |
|         | LE THK        | -.0020                  | -.0020        | -.0010  | -.0010  | -.0010  | -.0010  | -.0015  | -.0015  | -.0020  | -.0010  | -.0010  |
|         | TE THK        | -.0010                  | -.0020        | -.0010  | -.0010  | -.0020  | -.0010  | -.0010  | -.0020  | -.0020  | -.0010  | -.0010  |
| D-D     | CHORD         | + .0040                 | + .0035       | + .0040 | + .0030 | + .0030 | + .0060 | + .0050 | + .0035 | + .0035 | + .0040 | + .0040 |
|         | MAX THK       | -.0015                  | -.0015        | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0020  | -.0020  | -.0010  | -.0010  |
|         | LE THK        | -.0020                  | -.0015        | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0015  | -.0020  | -.0010  | -.0010  |
|         | TE THK        | -.0005                  | -.0005        | + .0005 | -.0010  | + .0005 | + .0005 | + .0005 | -.0005  | -.0005  | + .0000 | + .0000 |
| E-E     | CHORD         | + .0025                 | + .0020       | + .0035 | + .0015 | + .0015 | + .0050 | + .0040 | + .0020 | + .0020 | + .0030 | + .0025 |
|         | MAX THK       | + .0005                 | + .0010       | + .0005 | + .0005 | + .0010 | + .0010 | + .0005 | + .0000 | + .0000 | + .0010 | + .0010 |
|         | LE THK        | -.0015                  | -.0010        | -.0010  | -.0010  | -.0005  | -.0005  | -.0010  | -.0010  | -.0015  | -.0010  | -.0010  |
|         | TE THK        | + .0000                 | -.0010        | + .0000 | -.0010  | + .0000 | + .0000 | + .0000 | -.0010  | -.0010  | -.0005  | + .0000 |
| F-F     | CHORD         | + .0020                 | + .0020       | + .0030 | + .0010 | + .0010 | + .0050 | + .0030 | + .0030 | + .0020 | + .0035 | + .0035 |
|         | MAX THK       | -.0010                  | -.0010        | -.0010  | -.0005  | -.0005  | -.0005  | -.0010  | -.0010  | -.0010  | -.0005  | -.0005  |
|         | LE THK        | + .0000                 | + .0000       | + .0005 | + .0005 | + .0005 | + .0005 | + .0005 | + .0000 | + .0005 | + .0005 | + .0005 |
|         | TE THK        | -.0020                  | -.0025        | -.0020  | -.0025  | -.0020  | -.0020  | -.0025  | -.0025  | -.0030  | -.0020  | -.0020  |
| G-G     | CHORD         | + .0030                 | + .0030       | + .0040 | + .0035 | + .0035 | + .0060 | + .0045 | + .0035 | + .0035 | + .0050 | + .0050 |
|         | MAX THK       | -.0020                  | -.0020        | -.0015  | -.0020  | -.0015  | -.0015  | -.0020  | -.0020  | -.0020  | -.0015  | -.0015  |
|         | LE THK        | + .0000                 | + .0000       | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 |
|         | TE THK        | + .0000                 | + .0000       | + .0005 | + .0005 | + .0005 | + .0005 | + .0005 | + .0000 | + .0000 | + .0010 | + .0005 |
| H-H     | CHORD         | + .0060                 | + .0060       | + .0060 | + .0065 | + .0065 | + .0080 | + .0070 | + .0060 | + .0055 | + .0075 | + .0075 |
|         | MAX THK       | -.0020                  | -.0020        | -.0020  | -.0020  | -.0015  | -.0015  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  |
|         | LE THK        | + .0015                 | + .0015       | + .0015 | + .0015 | + .0015 | + .0015 | + .0015 | + .0010 | + .0010 | + .0015 | + .0020 |
|         | TE THK        | + .0005                 | + .0000       | + .0005 | + .0005 | + .0005 | + .0005 | + .0000 | + .0000 | + .0000 | + .0010 | + .0010 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |        |        |        |        |        |        |        |        |        |
|---------|------------|---------------------|---------------|--------|--------|--------|--------|--------|--------|--------|--------|--------|
|         |            |                     | 82            | 83     | 84     | 85     | 86     | 87     | 88     | 89     | 90     | 91     |
| B-B     | CHORD      | + .007              | -.0040        | -.0060 | -.0060 | -.0060 | -.0030 | -.0040 | -.0035 | -.0055 | -.0020 | -.0060 |
|         | MAX THK    | -.007               | -.0010        | -.0020 | -.0020 | -.0020 | -.0005 | -.0005 | -.0010 | -.0015 | -.0010 | -.0015 |
|         | LE THK     | -.002               | -.0025        | -.0030 | -.0030 | -.0035 | -.0020 | -.0020 | -.0020 | -.0035 | -.0030 | -.0035 |
|         | TE THK     | + .005              | -.0020        | -.0020 | -.0020 | -.0030 | -.0020 | -.0015 | -.0015 | -.0020 | -.0015 | -.0030 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| C-C     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0015 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| D-D     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| E-E     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| F-F     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| G-G     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |
| H-H     | CHORD      | -.002               | +.0005        | +.0010 | +.0010 | +.0010 | +.0015 | +.0015 | +.0010 | +.0010 | +.0000 | +.0025 |
|         | MAX THK    | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | LE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | TE THK     | -.002               | -.0010        | -.0020 | -.0020 | -.0020 | -.0010 | -.0010 | -.0010 | -.0010 | -.0010 | -.0020 |
|         | MAX THK    | -.002               | +.0005        | +.0000 | +.0000 | +.0000 | +.0005 | +.0010 | +.0000 | +.0005 | +.0000 | +.0005 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS.<br>TYPE | DRG.<br>TOLE-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|---------------|------------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |               |                        | 92            | 93      | 94      | 95      | 96      | 97      | 98      | 99      | 100     | 101     |
| B-B     | CHORD         | + .007                 | -.0055        | -.0060  | -.0040  | -.0060  | -.0040  | -.0070  | -.0045  | -.0060  | -.0055  | -.0050  |
|         |               | - .007                 |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK       | + .005                 | -.0015        | -.0010  | -.0010  | -.0015  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  |
|         |               | - .002                 |               |         |         |         |         |         |         |         |         |         |
|         | LE THK        | + .005                 | -.0030        | -.0030  | -.0030  | -.0045  | -.0035  | -.0035  | -.0030  | -.0040  | -.0035  | -.0030  |
|         |               | - .002                 |               |         |         |         |         |         |         |         |         |         |
|         | TE THK        | + .005                 | -.0030        | -.0030  | -.0025  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  |
|         |               | - .002                 |               |         |         |         |         |         |         |         |         |         |
| C-C     | CHORD         |                        | -.0010        | -.0010  | -.0010  | -.0020  | -.0020  | -.0020  | -.0010  | -.0015  | -.0010  | -.0005  |
|         | MAX THK       |                        | -.0030        | -.0025  | -.0025  | -.0025  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  |
|         | LE THK        |                        | -.0020        | -.0015  | -.0010  | -.0030  | -.0020  | -.0020  | -.0015  | -.0025  | -.0025  | -.0015  |
|         | TE THK        |                        | -.0020        | -.0015  | -.0015  | -.0015  | -.0030  | -.0020  | -.0020  | -.0020  | -.0025  | -.0020  |
| D-D     | CHORD         |                        | + .0030       | + .0025 | + .0045 | + .0025 | + .0020 | + .0020 | + .0035 | + .0035 | + .0035 | + .0045 |
|         | MAX THK       |                        | -.0020        | -.0015  | -.0010  | -.0015  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  |
|         | LE THK        |                        | -.0015        | -.0015  | -.0015  | -.0025  | -.0020  | -.0020  | -.0010  | -.0020  | -.0020  | -.0015  |
|         | TE THK        |                        | -.0005        | -.0005  | + .0000 | -.0005  | -.0005  | -.0010  | + .0000 | + .0000 | -.0010  | + .0000 |
| E-E     | CHORD         |                        | + .0020       | + .0010 | + .0030 | + .0020 | + .0010 | + .0050 | + .0030 | + .0020 | + .0020 | + .0030 |
|         | MAX THK       |                        | + .0005       | + .0005 | + .0005 | + .0010 | + .0010 | + .0000 | + .0005 | -.0005  | + .0000 | + .0000 |
|         | LE THK        |                        | -.0010        | -.0010  | -.0010  | -.0020  | -.0015  | -.0020  | -.0010  | -.0020  | -.0015  | -.0015  |
|         | TE THK        |                        | -.0010        | -.0010  | -.0005  | -.0010  | -.0010  | -.0015  | -.0010  | -.0010  | -.0015  | -.0010  |
| F-F     | CHORD         |                        | + .0020       | + .0010 | + .0035 | + .0015 | + .0010 | + .0005 | + .0030 | + .0020 | + .0020 | + .0030 |
|         | MAX THK       |                        | -.0015        | -.0010  | -.0005  | -.0005  | -.0015  | -.0015  | -.0010  | -.0015  | -.0015  | -.0015  |
|         | LE THK        |                        | -.0005        | + .0000 | + .0005 | -.0005  | -.0005  | + .0005 | + .0000 | -.0010  | -.0005  | + .0000 |
|         | TE THK        |                        | -.0030        | -.0030  | -.0020  | -.0025  | -.0030  | -.0030  | -.0025  | -.0030  | -.0030  | -.0025  |
| G-G     | CHORD         |                        | + .0040       | + .0020 | + .0045 | + .0030 | + .0025 | + .0020 | + .0050 | + .0040 | + .0045 | + .0040 |
|         | MAX THK       |                        | -.0025        | -.0020  | -.0015  | -.0015  | -.0020  | -.0025  | -.0015  | -.0025  | -.0025  | -.0020  |
|         | LE THK        |                        | -.0010        | -.0005  | + .0000 | -.0010  | -.0010  | -.0010  | -.0005  | -.0010  | -.0010  | -.0010  |
|         | TE THK        |                        | + .0000       | + .0000 | + .0005 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 |
| H-H     | CHORD         |                        | -.0065        | + .0060 | + .0070 | -.0050  | + .0050 | -.0055  | + .0080 | + .0055 | + .0070 | + .0060 |
|         | MAX THK       |                        | -.0020        | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  |
|         | LE THK        |                        | + .0010       | + .0010 | + .0015 | + .0010 | + .0010 | + .0005 | + .0015 | + .0005 | + .0010 | + .0010 |
|         | TE THK        |                        | + .0000       | + .0005 | + .0005 | + .0000 | + .0000 | + .0000 | + .0005 | + .0000 | + .0000 | + .0000 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOLE-RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|------------|------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                  | 102           | 103     | 104     | 105     | 106     | 107     | 108     | 110     | 111     | 112     |
| B-B     | CHORD      | + .007           | -.0050        | -.0070  | -.0070  | -.0050  | -.0070  | -.0060  | -.0040  | -.0055  | -.0050  | -.0055  |
|         |            | -.007            |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005           | -.0020        | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  |
|         |            | -.002            |               |         |         |         |         |         |         |         |         |         |
| C-C     | LE THK     | + .005           | -.0030        | -.0035  | -.0035  | -.0030  | -.0040  | -.0030  | -.0030  | -.0035  | -.0030  | -.0035  |
|         |            | -.002            |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005           | -.0030        | -.0040  | -.0030  | -.0030  | -.0040  | -.0030  | -.0020  | -.0030  | -.0030  | -.0030  |
|         |            | -.002            |               |         |         |         |         |         |         |         |         |         |
|         | CHORD      |                  | + .0000       | -.0030  | -.0025  | -.0010  | -.0015  | -.0010  | + .0000 | + .0000 | + .0000 | -.0005  |
|         | MAX THK    |                  | -.0030        | -.0035  | -.0035  | -.0035  | -.0035  | -.0030  | -.0030  | -.0035  | -.0030  | -.0030  |
| D-D     | LE THK     |                  | -.0020        | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  |
|         |            |                  | -.0020        | -.0025  | -.0025  | -.0025  | -.0025  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  |
|         | TE THK     |                  | + .0060       | + .0020 | + .0020 | + .0040 | + .0025 | + .0040 | + .0050 | + .0040 | + .0045 | + .0045 |
|         |            |                  | -.0020        | -.0020  | -.0020  | -.0020  | -.0025  | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  |
| E-E     | LE THK     |                  | -.0015        | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  |
|         |            |                  | + .0000       | -.0010  | -.0010  | -.0010  | -.0010  | -.0005  | -.0000  | -.0010  | + .0000 | -.0005  |
|         | TE THK     |                  | + .0030       | + .0005 | + .0005 | + .0020 | + .0010 | + .0020 | + .0035 | + .0020 | + .0030 | + .0030 |
|         |            |                  | + .0000       | + .0000 | + .0000 | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | + .0005 | + .0005 |
| F-F     | LE THK     |                  | -.0015        | -.0020  | -.0015  | -.0015  | -.0020  | -.0015  | -.0010  | -.0015  | -.0015  | -.0015  |
|         |            |                  | -.0010        | -.0020  | -.0015  | -.0015  | -.0020  | -.0015  | -.0005  | -.0015  | -.0005  | -.0010  |
|         | TE THK     |                  | + .0030       | + .0010 | + .0010 | + .0020 | + .0010 | + .0015 | + .0030 | + .0020 | + .0030 | + .0035 |
|         |            |                  | -.0010        | -.0015  | -.0010  | -.0010  | -.0010  | -.0005  | -.0005  | -.0005  | -.0005  | -.0005  |
| G-G     | LE THK     |                  | + .0000       | -.0010  | + .0000 | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | -.0005  | + .0000 |
|         |            |                  | -.0030        | -.0030  | -.0025  | -.0030  | -.0035  | -.0030  | -.0025  | -.0030  | -.0025  | -.0030  |
|         | TE THK     |                  | + .0050       | + .0020 | + .0025 | + .0035 | + .0020 | + .0030 | + .0045 | + .0040 | + .0050 | + .0045 |
|         |            |                  | -.0020        | -.0035  | -.0025  | -.0025  | -.0030  | -.0025  | -.0020  | -.0025  | -.0020  | -.0020  |
| H-H     | LE THK     |                  | -.0010        | -.0015  | -.0010  | -.0010  | -.0010  | -.0010  | -.0005  | -.0010  | -.0005  | -.0005  |
|         |            |                  | + .0000       | + .0005 | + .0000 | -.0005  | -.0010  | -.0005  | + .0000 | -.0005  | + .0000 | + .0000 |
|         | TE THK     |                  | + .0065       | + .0040 | + .0050 | + .0050 | + .0045 | + .0055 | + .0070 | + .0060 | + .0070 | + .0065 |
|         |            |                  | -.0020        | -.0025  | -.0020  | -.0020  | -.0025  | -.0025  | -.0020  | -.0025  | -.0020  | -.0020  |
|         | LE THK     |                  | + .0010       | + .0005 | + .0010 | + .0010 | + .0005 | + .0010 | + .0010 | + .0005 | + .0010 | + .0010 |
|         |            |                  | + .0000       | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 | + .0000 |
|         | TE THK     |                  | + .0000       | + .0000 | + .0000 | -.0005  | -.0010  | -.0005  | + .0000 | + .0000 | + .0000 | + .0000 |
|         |            |                  |               |         |         |         |         |         |         |         |         |         |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|------------|-----------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                 | 113           | 114     | 115     | 116     | 117     | 118     | 119     | 120     | 121     | 122     |
| B-B     | CHORD      | + .007          | - .0070       | - .0050 | - .0040 | - .0060 | - .0050 | - .0050 | - .0070 | - .0055 | - .0070 | - .0085 |
|         |            | - .007          |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005          | - .0015       | - .0010 | - .0015 | - .0010 | - .0020 | - .0015 | - .0020 | - .0020 | - .0020 | - .0020 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| C-C     | LE THK     | + .005          | - .0040       | - .0040 | - .0035 | - .0035 | - .0035 | - .0035 | - .0040 | - .0035 | - .0040 | - .0035 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005          | - .0040       | - .0030 | - .0035 | - .0030 | - .0040 | - .0030 | - .0040 | - .0030 | - .0040 | - .0040 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| D-D     | CHORD      | + .007          | - .0020       | - .0005 | + .0000 | - .0060 | - .0020 | - .0010 | - .0015 | - .0010 | - .0040 | - .0030 |
|         |            | - .007          |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005          | - .0030       | - .0030 | - .0030 | - .0035 | - .0035 | - .0035 | - .0040 | - .0035 | - .0035 | - .0040 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| E-E     | LE THK     | + .005          | - .0020       | - .0020 | - .0020 | - .0030 | - .0020 | - .0020 | - .0025 | - .0020 | - .0020 | - .0030 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005          | - .0020       | - .0005 | - .0010 | - .0010 | - .0010 | - .0010 | - .0005 | - .0010 | - .0010 | - .0010 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| F-F     | CHORD      | + .007          | - .0015       | + .0025 | + .0025 | - .0010 | + .0015 | + .0025 | + .0025 | + .0015 | + .0005 | - .0005 |
|         |            | - .007          |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005          | - .0000       | + .0005 | + .0000 | + .0000 | - .0005 | + .0000 | - .0005 | + .0000 | + .0000 | - .0005 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| G-G     | LE THK     | + .005          | - .0010       | - .0015 | - .0015 | - .0020 | - .0020 | - .0015 | - .0020 | - .0015 | - .0020 | - .0025 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005          | - .0010       | - .0010 | - .0010 | - .0010 | - .0015 | - .0010 | - .0010 | - .0010 | - .0015 | - .0020 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| H-H     | CHORD      | + .007          | - .0020       | + .0045 | + .0040 | - .0010 | + .0040 | + .0050 | + .0035 | + .0040 | + .0030 | + .0015 |
|         |            | - .007          |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK    | + .005          | - .0025       | - .0020 | - .0025 | - .0025 | - .0025 | - .0025 | - .0025 | - .0025 | - .0025 | - .0035 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
| I-I     | LE THK     | + .005          | - .0000       | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 | - .0010 | - .0005 | - .0010 | - .0015 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |
|         | TE THK     | + .005          | - .0000       | + .0000 | + .0000 | + .0015 | + .0000 | + .0000 | - .0005 | + .0000 | - .0005 | - .0010 |
|         |            | - .002          |               |         |         |         |         |         |         |         |         |         |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS.<br>TYPE | DRNG.<br>TOLE-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|---------------|-------------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |               |                         | 123           | 124     | 125     | 126     | 127     | 128     | 129     | 130     | 109     | 131     |
| B-B     | CHORD         | + .007                  | -.0060        | -.0060  | -.0070  | -.0040  | -.0060  | -.0065  | -.0065  | -.0055  | -.0035  | -.0045  |
|         |               | - .007                  |               |         |         |         |         |         |         |         |         |         |
|         | MAX THK       | + .005                  | -.0010        | -.0010  | -.0015  | -.0010  | -.0010  | -.0015  | -.0015  | -.0010  | -.0010  | -.0015  |
|         |               | - .002                  |               |         |         |         |         |         |         |         |         |         |
| C-C     | LE THK        | + .005                  | -.0030        | -.0030  | -.0035  | -.0025  | -.0030  | -.0035  | -.0035  | -.0035  | -.0030  | -.0035  |
|         |               | - .002                  |               |         |         |         |         |         |         |         |         |         |
|         | TE THK        | + .005                  | -.0040        | -.0040  | -.0030  | -.0030  | -.0030  | -.0040  | -.0030  | -.0030  | -.0030  | -.0030  |
|         |               | - .002                  |               |         |         |         |         |         |         |         |         |         |
| D-D     | CHORD         |                         | -.0020        | -.0005  | -.0010  | + .0005 | -.0005  | -.0010  | -.0020  | + .0000 | + .0010 | -.0015  |
|         | MAX THK       |                         | -.0030        | -.0030  | -.0030  | -.0030  | -.0025  | -.0025  | -.0035  | -.0030  | -.0030  | -.0035  |
|         | LE THK        |                         | -.0015        | -.0020  | -.0025  | -.0010  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  |
|         | TE THK        |                         | -.0025        | -.0020  | -.0020  | -.0020  | -.0020  | -.0020  | -.0025  | -.0015  | -.0010  | -.0020  |
| E-E     | CHORD         |                         | + .0030       | + .0045 | + .0030 | + .0050 | + .0040 | + .0035 | + .0040 | + .0045 | + .0055 | + .0040 |
|         | MAX THK       |                         | -.0020        | -.0020  | -.0020  | -.0015  | -.0020  | -.0020  | -.0020  | -.0015  | -.0015  | -.0020  |
|         | LE THK        |                         | -.0015        | -.0020  | -.0020  | + .0000 | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  |
|         | TE THK        |                         | -.0010        | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | -.0010  | + .0000 | + .0000 | -.0005  |
| F-F     | CHORD         |                         | + .0015       | + .0020 | + .0020 | + .0040 | + .0025 | + .0020 | + .0020 | + .0030 | + .0040 | + .0020 |
|         | MAX THK       |                         | + .0005       | + .0000 | + .0000 | + .0010 | + .0005 | + .0000 | + .0000 | + .0005 | + .0005 | + .0000 |
|         | LE THK        |                         | -.0010        | -.0010  | -.0020  | -.0010  | -.0005  | -.0015  | -.0020  | -.0005  | -.0010  | -.0015  |
|         | TE THK        |                         | -.0010        | -.0010  | -.0020  | -.0010  | -.0010  | -.0010  | -.0015  | -.0010  | -.0010  | -.0010  |
| G-G     | CHORD         |                         | + .0020       | + .0030 | + .0020 | + .0040 | + .0020 | + .0020 | + .0020 | + .0020 | + .0045 | + .0025 |
|         | MAX THK       |                         | + .0000       | + .0000 | -.0005  | + .0000 | -.0005  | -.0015  | -.0010  | + .0000 | + .0000 | + .0000 |
|         | LE THK        |                         | + .0000       | + .0000 | -.0005  | -.0005  | + .0000 | + .0000 | -.0010  | + .0000 | + .0000 | + .0000 |
|         | TE THK        |                         | -.0030        | -.0030  | -.0030  | -.0025  | -.0030  | -.0030  | -.0030  | -.0025  | -.0025  | -.0030  |
| H-H     | CHORD         |                         | + .0007       | + .0055 | + .0040 | + .0050 | + .0035 | + .0035 | + .0050 | + .0050 | + .0000 | + .0050 |
|         | MAX THK       |                         | -.0025        | -.0025  | -.0025  | -.0020  | -.0025  | -.0025  | -.0025  | -.0020  | -.0020  | -.0025  |
|         | LE THK        |                         | -.0005        | -.0005  | -.0010  | + .0000 | -.0010  | -.0010  | -.0010  | -.0005  | + .0000 | -.0005  |
|         | TE THK        |                         | + .0000       | + .0000 | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | + .0000 | + .0005 | + .0000 |
|         | CHORD         |                         | + .0060       | + .0080 | + .0060 | + .0080 | + .0060 | + .0060 | + .0070 | + .0070 | + .0090 | + .0080 |
|         | MAX THK       |                         | -.0020        | -.0025  | -.0015  | -.0015  | -.0020  | -.0020  | -.0020  | -.0020  | -.0015  | -.0020  |
|         | LE THK        |                         | + .0010       | + .0010 | + .0005 | + .0015 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 |
|         | TE THK        |                         | + .0000       | + .0005 | + .0000 | + .0010 | + .0000 | + .0000 | + .0000 | + .0005 | + .0000 | + .0000 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Continued).

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |         |         |         |         |         |         |         |         |         |
|---------|------------|---------------------|---------------|---------|---------|---------|---------|---------|---------|---------|---------|---------|
|         |            |                     | 132           | 133     | 134     | 135     | 136     | 137     | 138     | 139     | 140     | 141     |
| B-B     | CHORD      | + .007<br>-.007     | -.0040        | -.0025  | -.0035  | -.0050  | -.0045  | -.0050  | -.0060  | -.0055  | -.0040  | -.0020  |
|         | MAX THK    | + .005<br>-.002     | -.0010        | -.0010  | -.0015  | -.0020  | -.0015  | -.0015  | -.0020  | -.0010  | -.0015  | + .0000 |
|         | LE THK     | + .005<br>-.002     | -.0080        | -.0030  | -.0030  | -.0030  | -.0030  | -.0035  | -.0040  | -.0035  | -.0030  | -.0020  |
|         | TE THK     | + .005<br>-.002     | -.0035        | -.0025  | -.0030  | -.0030  | -.0040  | -.0030  | -.0030  | -.0030  | -.0020  | -.0020  |
| C-C     | CHORD      |                     | + .0000       | + .0015 | + .0015 | + .0000 | + .0000 | + .0000 | -.0010  | + .0000 | + .0000 | + .0005 |
|         | MAX THK    |                     | -.0040        | -.0030  | -.0035  | -.0035  | -.0035  | -.0035  | -.0040  | -.0030  | -.0030  | -.0025  |
|         | LE THK     |                     | -.0015        | -.0015  | -.0015  | -.0020  | -.0020  | -.0025  | -.0025  | -.0020  | -.0020  | -.0015  |
|         | TE THK     |                     | -.0010        | -.0015  | -.0020  | -.0025  | -.0020  | -.0020  | -.0020  | -.0020  | -.0010  | -.0020  |
| D-D     | CHORD      |                     | + .0050       | + .0070 | + .0060 | + .0040 | + .0050 | + .0050 | + .0035 | + .0040 | + .0045 | + .0050 |
|         | MAX THK    |                     | -.0015        | -.0015  | -.0020  | -.0020  | -.0020  | -.0020  | -.0025  | -.0020  | -.0020  | -.0010  |
|         | LE THK     |                     | -.0010        | -.0015  | -.0015  | -.0015  | -.0015  | -.0015  | -.0020  | -.0010  | -.0010  | -.0010  |
|         | TE THK     |                     | + .0010       | + .0000 | -.0010  | -.0010  | -.0010  | -.0005  | -.0010  | -.0010  | + .0000 | + .0000 |
| E-E     | CHORD      |                     | + .0050       | + .0050 | + .0045 | + .0030 | + .0040 | + .0035 | + .0020 | + .0025 | + .0040 | + .0040 |
|         | MAX THK    |                     | + .0010       | + .0005 | + .0000 | + .0000 | + .0005 | + .0000 | -.0005  | + .0000 | + .0000 | + .0015 |
|         | LE THK     |                     | -.0010        | -.0010  | -.0015  | -.0015  | -.0010  | -.0015  | -.0015  | -.0010  | -.0010  | -.0010  |
|         | TE THK     |                     | + .0000       | -.0005  | -.0010  | -.0015  | -.0010  | -.0010  | -.0020  | -.0010  | + .0000 | + .0000 |
| F-F     | CHORD      |                     | + .0045       | + .0050 | + .0040 | + .0030 | + .0035 | + .0030 | + .0020 | + .0020 | + .0035 | + .0030 |
|         | MAX THK    |                     | + .0000       | + .0000 | -.0005  | -.0005  | + .0000 | -.0005  | -.0010  | -.0005  | + .0000 | + .0005 |
|         | LE THK     |                     | + .0005       | + .0000 | + .0000 | + .0000 | -.0005  | + .0000 | -.0010  | -.0005  | + .0000 | + .0000 |
|         | TE THK     |                     | -.0020        | -.0025  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  | -.0030  | -.0025  | -.0030  |
| G-G     | CHORD      |                     | + .0060       | + .0070 | + .0060 | + .0045 | + .0050 | + .0050 | + .0040 | + .0040 | + .0045 | + .0040 |
|         | MAX THK    |                     | -.0015        | -.0020  | -.0020  | -.0025  | -.0025  | -.0025  | -.0025  | -.0020  | -.0020  | -.0020  |
|         | LE THK     |                     | + .0000       | + .0000 | -.0010  | -.0010  | -.0005  | -.0010  | -.0010  | -.0005  | -.0005  | + .0000 |
|         | TE THK     |                     | + .0005       | + .0000 | -.0005  | -.0005  | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | -.0010  |
| H-H     | CHORD      |                     | + .0080       | + .0090 | + .0005 | + .0070 | + .0080 | + .0070 | + .0065 | + .0065 | + .0070 | + .0060 |
|         | MAX THK    |                     | -.0015        | -.0015  | -.0020  | -.0020  | -.0020  | -.0020  | -.0025  | -.0020  | -.0020  | -.0025  |
|         | LE THK     |                     | + .0015       | + .0015 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0010 | + .0015 | + .0010 |
|         | TE THK     |                     | + .0005       | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | -.0005  | + .0000 | + .0000 | + .0000 |

Table 5. Geometry Summary, Stage 5 ECM'd Airfoil, Part No. 4013148-505P01 (Concluded).

| SECTION | MEAS. TYPE | DRNG. TOL-<br>RANCE | SERIAL NUMBER |  |  |  |  |  |  |  |  |  |
|---------|------------|---------------------|---------------|--|--|--|--|--|--|--|--|--|
|         |            |                     | 142           |  |  |  |  |  |  |  |  |  |
| B-B     | CHORD      | + .007              | - .0035       |  |  |  |  |  |  |  |  |  |
|         |            | - .007              |               |  |  |  |  |  |  |  |  |  |
|         | MAX THK    | + .005              | + .0000       |  |  |  |  |  |  |  |  |  |
|         |            | - .002              |               |  |  |  |  |  |  |  |  |  |
|         | LE THK     | + .005              | - .0020       |  |  |  |  |  |  |  |  |  |
|         |            | - .002              |               |  |  |  |  |  |  |  |  |  |
|         | TE THK     | + .005              | - .0020       |  |  |  |  |  |  |  |  |  |
|         |            | - .002              |               |  |  |  |  |  |  |  |  |  |
| C-C     | CHORD      |                     | + .0000       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | - .0025       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | - .0015       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | - .0020       |  |  |  |  |  |  |  |  |  |
| D-D     | CHORD      |                     | + .0045       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | - .0010       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | - .0010       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | - .0005       |  |  |  |  |  |  |  |  |  |
| E-E     | CHORD      |                     | + .0030       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | + .0010       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | - .0010       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | - .0010       |  |  |  |  |  |  |  |  |  |
| F-F     | CHORD      |                     | + .0025       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | + .0005       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | + .0000       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | - .0025       |  |  |  |  |  |  |  |  |  |
| G-G     | CHORD      |                     | + .0035       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | - .0020       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | + .0000       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | + .0000       |  |  |  |  |  |  |  |  |  |
| H-H     | CHORD      |                     | + .0070       |  |  |  |  |  |  |  |  |  |
|         | MAX THK    |                     | - .0025       |  |  |  |  |  |  |  |  |  |
|         | LE THK     |                     | + .0010       |  |  |  |  |  |  |  |  |  |
|         | TE THK     |                     | + .0000       |  |  |  |  |  |  |  |  |  |

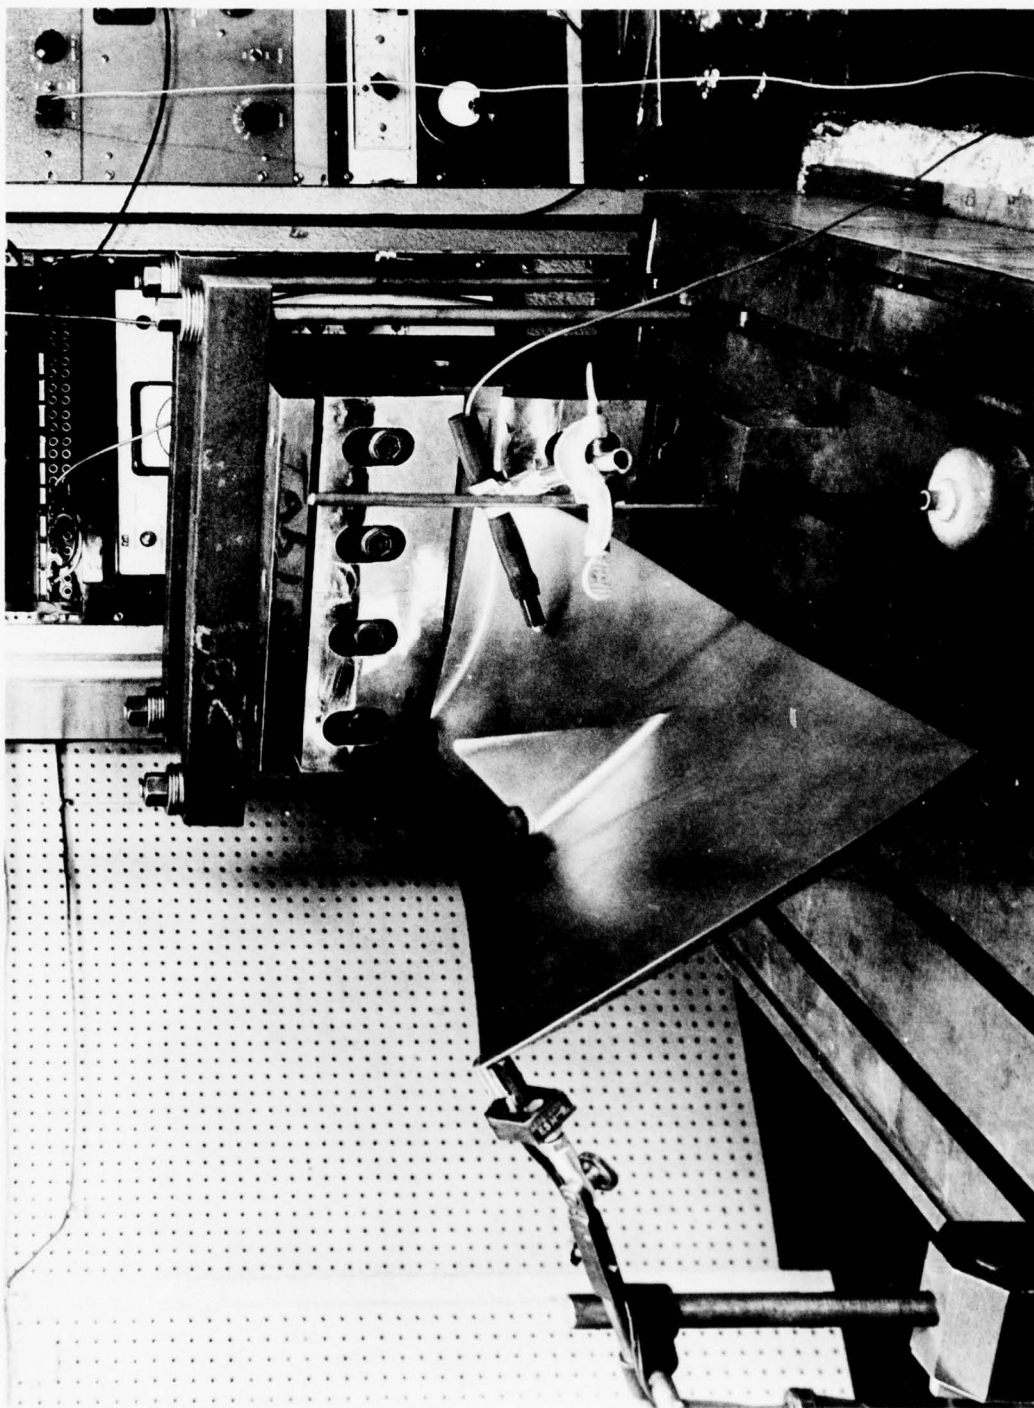


Figure 4. Typical Test Setup for Natural Frequencies and Nodal Patterns.

Table 6. ECM'd Stage 2 Blades, Part No. 4013148-502.

| Item           | Mode Number |        |        |        |        |        |        |        |         |         |         |
|----------------|-------------|--------|--------|--------|--------|--------|--------|--------|---------|---------|---------|
|                | 1           | 2      | 3      | 4      | 5      | 6      | 7      | 8      | 9       | 10      | 11      |
| S/N 367        | 794         | 2534   | 3370   | 5554   | 6320   | 7480   | 7916   | 9848   | 12034   | 12714   | 14356   |
| 131            | 806         | 2558   | 3330   | 5504   | 6332   | 7480   | 7784   | 9540   | 11640   | 12286   | 13834   |
| 168            | 792         | 2502   | 3330   | 5492   | 6128   | 7496   | 7938   | 9806   | 12302   | 12726   | 14556   |
| 115            | 804         | 2552   | 3388   | 5554   | 6160   | 7622   | 8002   | 9888   | 12374   | 12780   | 14662   |
| 354            | 786         | 2506   | 3388   | 5646   | 6242   | 7664   | 8056   | 10024  | 12392   | 13028   | 14958   |
| 187            | 788         | 2476   | 3304   | 5432   | 6090   | 7406   | 7770   | 9576   | 12370   | ---     | 14262   |
| 139            | 790         | 2522   | 3380   | 5576   | 6162   | 7668   | 8090   | 10014  | 12626   | 12978   | 15048   |
| 121            | 792         | 2536   | 3396   | 5570   | ---    | 7648   | 8096   | 9936   | 12480   | 12822   | 14914   |
| 357            | 766         | 2470   | 3298   | 5410   | 6202   | 7410   | 7700   | 9508   | 12212   | 12376   | 14312   |
| 356            | 820         | 2594   | 3504   | 5760   | 6326   | 7840   | 8280   | 10286  | 12684   | 13484   | 15420   |
| 155            | 796         | 2518   | 3386   | 5580   | 6120   | 7630   | 8044   | 9986   | 12594   | 12950   | ---     |
| 149            | 798         | 2522   | 3376   | 5520   | ---    | 7494   | 7950   | 9790   | 12224   | 12754   | 14368   |
| 107            | 784         | 2496   | 3332   | 5496   | 6076   | 7544   | 7988   | 9832   | 12368   | 12696   | 14662   |
| 358            | 804         | 2572   | 3414   | 5638   | 6120   | 7760   | 8232   | 10108  | 12804   | 13210   | 15334   |
| 159            | 796         | 2538   | 3348   | 5512   | ---    | 7582   | 7984   | 9848   | 12376   | 12754   | 14696   |
| No. of Samples | 15          | 15     | 15     | 15     | 12     | 15     | 15     | 15     | 15      | 14      | 14      |
| Unbiased: Mean | 794.4       | 2526.4 | 3369.6 | 5549.6 | 6189.8 | 7581.6 | 7988.7 | 9866   | 12365.3 | 12825.6 | 14670.1 |
| Std Dev        | 12.10       | 34.18  | 50.90  | 87.56  | 93.78  | 124.95 | 159.47 | 212.36 | 281.79  | 304.55  | 437.29  |

NOTE: All frequencies in Hertz.

Table 7. Conventional Stage 2 Blades, Part No. 4013148-502.

| Item           | Mode Number |      |      |      |      |      |      |       |       |       |       |
|----------------|-------------|------|------|------|------|------|------|-------|-------|-------|-------|
|                | 1           | 2    | 3    | 4    | 5    | 6    | 7    | 8     | 9     | 10    | 11    |
| S/N 107        | 812         | 2596 | 3566 | 5694 | 6130 | 7726 | 8236 | 10216 | 12276 | 13322 | 14754 |
| 103            | 802         | 2562 | 3550 | 5528 | 6138 | 7680 | 8124 | 10176 | 12250 | 13216 | 14800 |
| 105            | 802         | 2546 | 3524 | 5678 | 6102 | 7802 | 8214 | 10484 | 12332 | 13410 | 15218 |
| 114            | 818         | 2582 | 3530 | 5680 | 6154 | 7762 | 8262 | 10546 | 12476 | 13500 | 14972 |
| 109            | 806         | 2562 | 3504 | 5630 | 6168 | 7822 | 8168 | 10144 | 12308 | 13092 | 15096 |
| 101            | 822         | 2594 | 3548 | 5686 | 6208 | 7816 | 8190 | 10526 | 12486 | 13492 | 15238 |
| 110            | 806         | 2570 | 3458 | 5618 | 6156 | 7742 | 8182 | 10230 | ---   | 13160 | 15050 |
| 113            | 794         | 2546 | 3446 | 5636 | 6228 | 7802 | 8206 | 10272 | 12448 | 13400 | 15216 |
| 108            | 790         | 2522 | 3420 | 5550 | 6100 | 7656 | 8036 | 10096 | 12248 | 12866 | 14836 |
| 104            | 804         | 2578 | 3202 | 5724 | 6292 | 7680 | 8128 | 10228 | 12296 | 13214 | 14848 |
| 106            | 776         | 2504 | 3382 | 5524 | 6028 | 7584 | 7972 | 9962  | 12250 | 12714 | 14716 |
| 115            | 826         | 2586 | 3552 | 5688 | 6238 | 7722 | 8240 | 10420 | 12292 | 13386 | 14850 |
| 102            | 800         | 2574 | 3486 | 5744 | 6200 | 7852 | 8406 | 10434 | 12438 | 13722 | 15186 |
| 111            | 810         | 2588 | 3506 | 5672 | 6158 | 7724 | 8224 | 10458 | 12408 | 13416 | 14828 |
| 112            | 828         | 2602 | 3516 | 5720 | 6168 | 7852 | 8268 | 10450 | 12424 | 13482 | 15158 |
| No. of Samples | 15          | 15   | 15   | 15   | 15   | 15   | 15   | 15    | 14    | 15    | 15    |
| Unbiased: Mean | 806         | 2568 | 3481 | 5652 | 6165 | 7748 | 8190 | 10310 | 12352 | 13293 | 14984 |
| Std Dev        | 14          | 28   | 93   | 70   | 64   | 78   | 102  | 177   | 90    | 259   | 189   |

NOTE: All frequencies in Hertz.

Table 8. ECN'd Stage 5 Blades, Part No. 4013148-505.

| Item                                                    | Mode Number |      |      |      |       |       |       |       |
|---------------------------------------------------------|-------------|------|------|------|-------|-------|-------|-------|
|                                                         | 1           | 2    | 3    | 4    | 5     | 6     | 7     | 8     |
| S/N 71                                                  | 1678        | 4226 | 5578 | 6700 | 9360  | 12536 | 13550 | 16976 |
| 127                                                     | 1664        | 4204 | 5108 | 6450 | 9324  | 12442 | 13172 | 16802 |
| 33                                                      | 1684        | 4224 | 5172 | 6502 | 9388  | 12600 | 13306 | 17060 |
| 123                                                     | 1676        | 4218 | 5610 | 6790 | 9340  | 12354 | 13632 | 17052 |
| 77                                                      | 1666        | 4212 | 5514 | 6608 | 9346  | 12604 | 13630 | 17108 |
| 139                                                     | 1680        | 4238 | 5466 | 6620 | 9320  | 12566 | 13466 | 16938 |
| 58                                                      | 1678        | 4226 | 5192 | 6488 | 9408  | 12606 | 13428 | 17166 |
| 41                                                      | 1680        | 4232 | 5460 | 6668 | 9348  | 12602 | 13542 | 18064 |
| 30                                                      | 1702        | 4290 | 5556 | 6722 | 9478  | 12776 | 13598 | 17284 |
| 48                                                      | 1684        | 4242 | 5478 | 6618 | 9424  | 12674 | 13556 | 17238 |
| 66                                                      | 1664        | 4198 | 5270 | 6512 | 9318  | 12496 | 13344 | 17056 |
| 112                                                     | 1662        | 4182 | 5038 | 6448 | 9216  | 12906 | 13204 | 16858 |
| 132                                                     | 1664        | 4206 | 5362 | 6524 | 9362  | 12568 | 13430 | 17024 |
| 61                                                      | 1686        | 4240 | 5462 | 6662 | 9376  | 12566 | 13536 | 17032 |
| 39                                                      | 1690        | 4244 | 5476 | 6654 | 9368  | 12632 | 13470 | 17006 |
| 137                                                     | 1658        | 4168 | 5272 | 6518 | 9372  | 12446 | 13396 | 16912 |
| 53                                                      | 1674        | 4222 | 5168 | 6454 | 9364  | 12608 | 13350 | 17008 |
| 94                                                      | 1666        | 4200 | 5278 | 6538 | 9358  | 12562 | 13412 | 17040 |
| 28                                                      | 1680        | 4244 | 5388 | 6558 | 9444  | 12694 | 13508 | 17212 |
| 37                                                      | 1670        | 4144 | 4698 | 6356 | 9294  | 12394 | 13434 | 16978 |
| No. of Samples                                          | 20          | 20   | 20   | 20   | 20    | 20    | 20    | 20    |
| Unbiased: Mean                                          | 1675        | 4218 | 5327 | 6570 | 9360  | 1258  | 13448 | 17041 |
| Std Dev                                                 | 11          | 31   | 222  | 110  | 56    | 127   | 129   | 121   |
| Mean*                                                   | 1731        | 4470 | 5722 | 6917 | 10024 | 12668 | 13937 | ---   |
| Std Dev*                                                | 10          | 48   | 49   | 45   | 255   | 368   | 286   | ---   |
| * 26 Blade Sampl, PM R95<br>Note: All Frequencies in Hz |             |      |      |      |       |       |       |       |

Table 9. Conventional Stage 5 Blades, Part No. 4013148-505.

| Item           | Mode Number |      |      |      |       |       |       |       |       |       |       |
|----------------|-------------|------|------|------|-------|-------|-------|-------|-------|-------|-------|
|                | 1           | 2    | 3    | 4    | 5     | 6     | 7     | 8     | 9     | 10    | 11    |
| S/N 151        | 1572        | 4213 | 5173 | 6437 | 9810  | 12956 | 14348 | 15564 | 17441 | 18216 | 19170 |
| 143            | 1675        | 4390 | 5309 | 6510 | 9939  | 13114 | 14763 | 16056 | 17882 | 18485 | 19770 |
| 152            | 1618        | 4268 | 5076 | 6432 | 9959  | 13020 | 14592 | 16159 | 17253 | 18305 | 19251 |
| 153            | 1624        | 4295 | 5121 | 6438 | 10027 | 13015 | 14656 | 16035 | 17517 | 18398 | 19286 |
| 144            | 1582        | 4214 | 5057 | ---  | 9932  | 13211 | 14699 | 16180 | 17432 | 18393 | 19418 |
| 148            | 1612        | 4290 | 5154 | ---  | 9830  | 13306 | 14612 | 15883 | 16717 | 18238 | 19403 |
| 156            | 1553        | 4222 | 5048 | 6513 | 9884  | 13108 | 14631 | 15823 | 17735 | 18418 | 19585 |
| 157            | 1616        | 4252 | 5248 | 6362 | 9402  | 12722 | 13873 | 15684 | 17020 | 17739 | 19526 |
| 154            | 1707        | 4378 | 5380 | ---  | 9476  | 12785 | 14043 | 15827 | 17419 | 17973 | 20022 |
| 150            | 1613        | 4281 | 5208 | 6519 | 9932  | 13231 | 14833 | 16318 | 17562 | 18485 | 19572 |
| 149            | 1581        | 4308 | 5179 | ---  | 9864  | 13186 | 14845 | 16106 | 17763 | 18479 | 19683 |
| 147            | 1643        | 4336 | 5308 | 6501 | 9727  | 13135 | 14397 | 15780 | 17024 | 18159 | 19691 |
| 158            | 1615        | 4312 | 5154 | 6642 | 10215 | 13465 | 14812 | 16457 | 17783 | 18530 | 19892 |
| 155            | 1608        | 4294 | 5217 | 6648 | 10242 | 13387 | 14911 | 16246 | 17639 | 18389 | 19675 |
| 145            | 1627        | 4261 | 5162 | 6536 | 9952  | 13158 | 14519 | 16317 | 17867 | 18496 | 20043 |
| 159            | 1618        | 4299 | 5088 | 6543 | 9980  | 13167 | 14791 | 16529 | 17781 | 18410 | 19871 |
| 161            | 1612        | 4297 | 5163 | 6451 | 9795  | 13192 | 14729 | 15963 | 17692 | 18414 | 19683 |
| 141            | 1592        | 4255 | 5155 | 6432 | 9987  | 13398 | 15158 | 16215 | 17834 | 18591 | 19717 |
| 146            | 1590        | 4279 | 5032 | 6371 | 9633  | 13356 | 14513 | 15868 | 17970 | 19429 | 21046 |
| 140            | 1583        | 4265 | 5199 | 6580 | 10269 | 13401 | 14992 | 16288 | 17661 | 18654 | 19767 |
| No. of Samples | 20          | 20   | 20   | 17   | 20    | 20    | 20    | 20    | 20    | 20    | 20    |
| Unbiased: Mean | 1614        | 4286 | 5177 | 6495 | 9293  | 13166 | 14636 | 16065 | 17550 | 18421 | 19718 |
| Std Dev        | 34.8        | 46.7 | 93.4 | 81.4 | 223.1 | 198.4 | 303.1 | 261.7 | 330.8 | 322.9 | 380.9 |

NOTE: All frequencies in Hertz.

Table 10. ECM'd Stage 8 Blades, Part No. 4013148-508.

| Item                            | Mode Number |            |              |              |              |                      |       |
|---------------------------------|-------------|------------|--------------|--------------|--------------|----------------------|-------|
|                                 | 1           | 2          | 3            | 4            | 5            | 6                    | 7     |
| S/N 119                         | 2558        | 5512       | 10850        | 13790        | 15268        | ---                  | ---   |
| 141                             | 2590        | 5610       | 10092        | 14130        | 15414        | ---                  | ---   |
| 58                              | 2556        | 5528       | 10212        | 13626        | ---          | ---                  | ---   |
| 29                              | 2632        | 5646       | 10340        | 13866        | 15924        | ---                  | ---   |
| 112                             | 2550        | 5580       | 9958         | 13524        | ---          | ---                  | ---   |
| 33                              | 2564        | 5490       | 9966         | 13544        | 15074        | 16224                | ---   |
| 93                              | 2638        | 5662       | 10346        | 14018        | 15766        | ---                  | ---   |
| 123                             | 2618        | 5636       | 10230        | 13902        | 15432        | 16592                | ---   |
| 153                             | 2654        | 5664       | 10368        | 14174        | 15550        | 16174                | ---   |
| 147                             | 2702        | 5752       | 10254        | 14084        | ---          | 16796                | 17256 |
| 63                              | 2552        | 5516       | 9942         | 13502        | 15690        | ---                  | ---   |
| 138                             | 2626        | 5442       | 10354        | 14116        | ---          | 16500                | ---   |
| 133                             | 2608        | 5544       | 10250        | 13940        | 15756        | ---                  | ---   |
| 111                             | 2636        | 5620       | 10190        | 13738        | ---          | 16270                | 16868 |
| 115                             | 2628        | 5616       | 10274        | 13612        | 15612        | 16480                | 19114 |
| 150                             | 2692        | 5726       | 10410        | 14288        | ---          | 16884                | ---   |
| 90                              | 2673        | 5682       | 10520        | 13914        | 15780        | ---                  | ---   |
| 96                              | 2642        | 5646       | 10400        | 14064        | 15792        | ---                  | ---   |
| 131                             | 2614        | 5612       | 10034        | 13498        | 15562        | ---                  | ---   |
| 113                             | 2646        | 5722       | 10144        | 13986        | ---          | 16468                | ---   |
| No. of Samples                  | 20          | 20         | 20           | 20           | 13           | 6                    | 1     |
| Unbiased:<br>Mean<br>Std Dev    | 2619<br>84  | 5610<br>84 | 10257<br>214 | 13841<br>272 | 15586<br>239 | Insufficient<br>Data |       |
| NOTE: All frequencies in Hertz. |             |            |              |              |              |                      |       |

Table 11. Conventional Stage 8 Blades, Part No. 4013148-508.

| Item                            | Mode Number |      |       |       |       |       |       |
|---------------------------------|-------------|------|-------|-------|-------|-------|-------|
|                                 | 1           | 2    | 3     | 4     | 5     | 6     | 7     |
| S/N 114                         | 2684        | 5645 | 10950 | 14596 | 16038 | 17064 | 19820 |
| 136                             | 2695        | 5705 | 11012 | 14752 | 16578 | 17435 | 20479 |
| 5                               | 2710        | 5691 | 10904 | 14584 | 15947 | 17258 | 19815 |
| 116                             | 2648        | 5669 | 10926 | 14738 | 16303 | 17877 | 20413 |
| 140                             | 2800        | 5859 | 11163 | 14853 | 16352 | 17858 | 20328 |
| 137                             | 2639        | 5583 | 10870 | 14728 | 15979 | 17559 | 21105 |
| 24                              | 2706        | 5633 | 10804 | 14252 | 15651 | 17323 | 20729 |
| 34                              | 2814        | 5845 | 11078 | 14577 | 16186 | 17693 | 20763 |
| 100                             | 2762        | 5768 | 10969 | 14725 | 16225 | 17893 | 20687 |
| 35                              | 2670        | 5650 | 10674 | 14486 | 16090 | 17556 | 20807 |
| 141                             | 2571        | 5527 | 10680 | 14245 | 15771 | 17371 | ---   |
| 26                              | 2730        | 5687 | 10799 | 14386 | 15954 | 17442 | 20880 |
| 132                             | 2679        | 5753 | 11025 | 14926 | 16384 | 17716 | 21212 |
| 149                             | 2749        | 5680 | 10972 | 14617 | 15880 | 17522 | 21030 |
| 151                             | 2719        | 5750 | 11002 | 14550 | 16158 | 17764 | 19652 |
| 123                             | 2640        | 5501 | 10647 | 13965 | 15406 | 17548 | ---   |
| 3                               | 2685        | 5703 | 10826 | 14556 | 15920 | 17105 | 21952 |
| 84                              | 2816        | 5843 | 11200 | 14770 | 16450 | 17570 | 22210 |
| 22                              | 2574        | 5572 | 10740 | 14484 | 16101 | 17532 | 22214 |
| 152                             | 2781        | 5804 | 11076 | 14327 | 16062 | 17358 | 20620 |
| No. of Samples                  | 20          | 20   | 20    | 20    | 20    | 20    | 18    |
| Unbiased:                       |             |      |       |       |       |       |       |
| Mean                            | 2704        | 5693 | 10917 | 14556 | 16072 | 17522 | 20818 |
| Std Dev                         | 71          | 102  | 157   | 234   | 279   | 237   | 744   |
| NOTE: All frequencies in Hertz. |             |      |       |       |       |       |       |

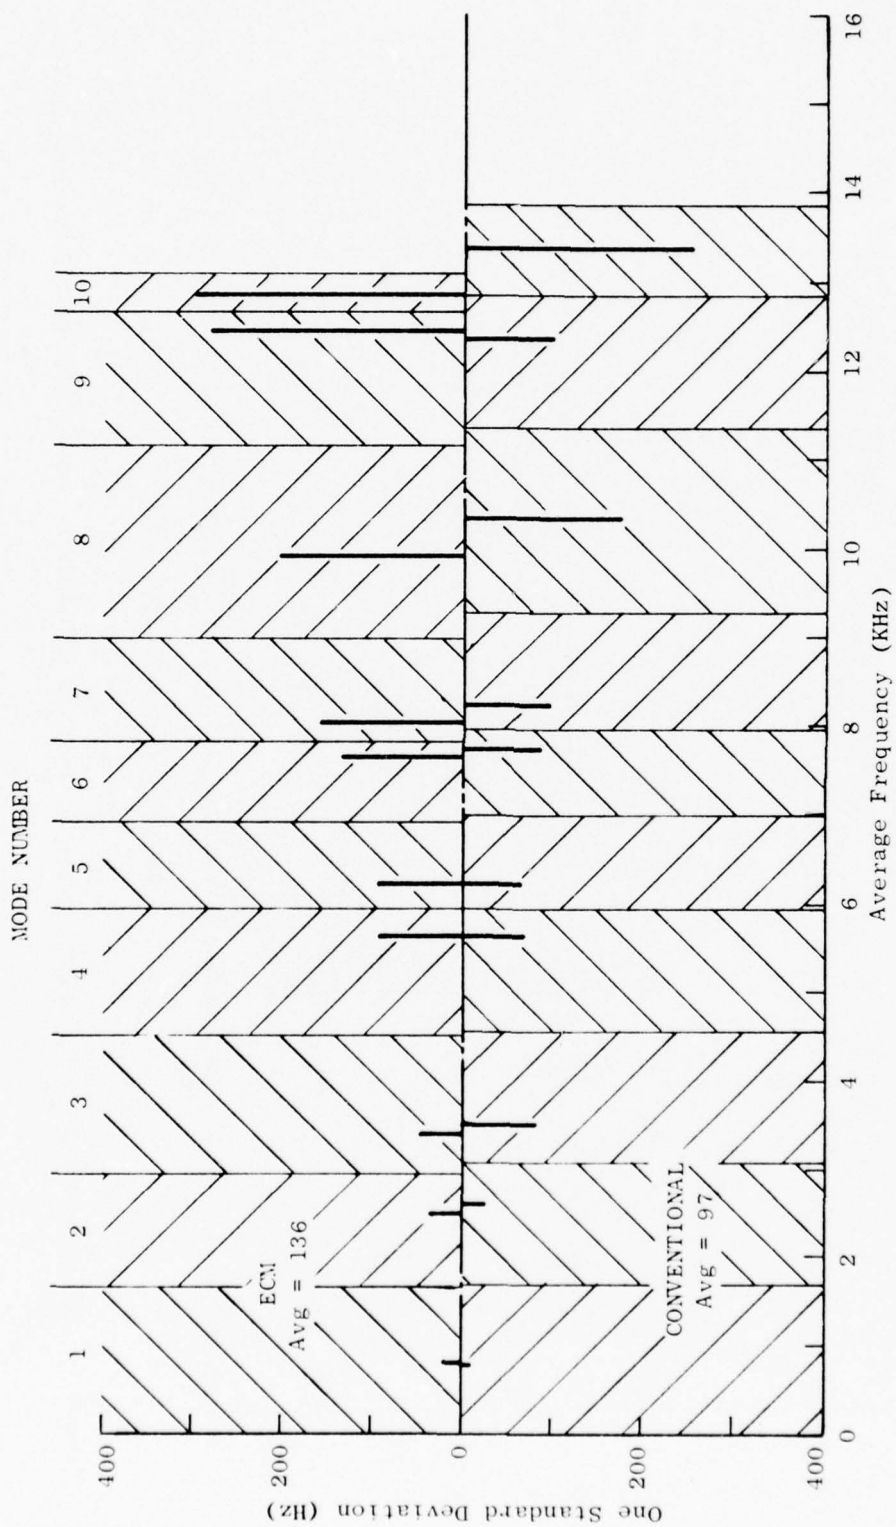


Figure 5. Resonant Frequency Summary, Stage 2 (Part No. 4013148-502P01), Standard Deviation Versus Average Frequency.

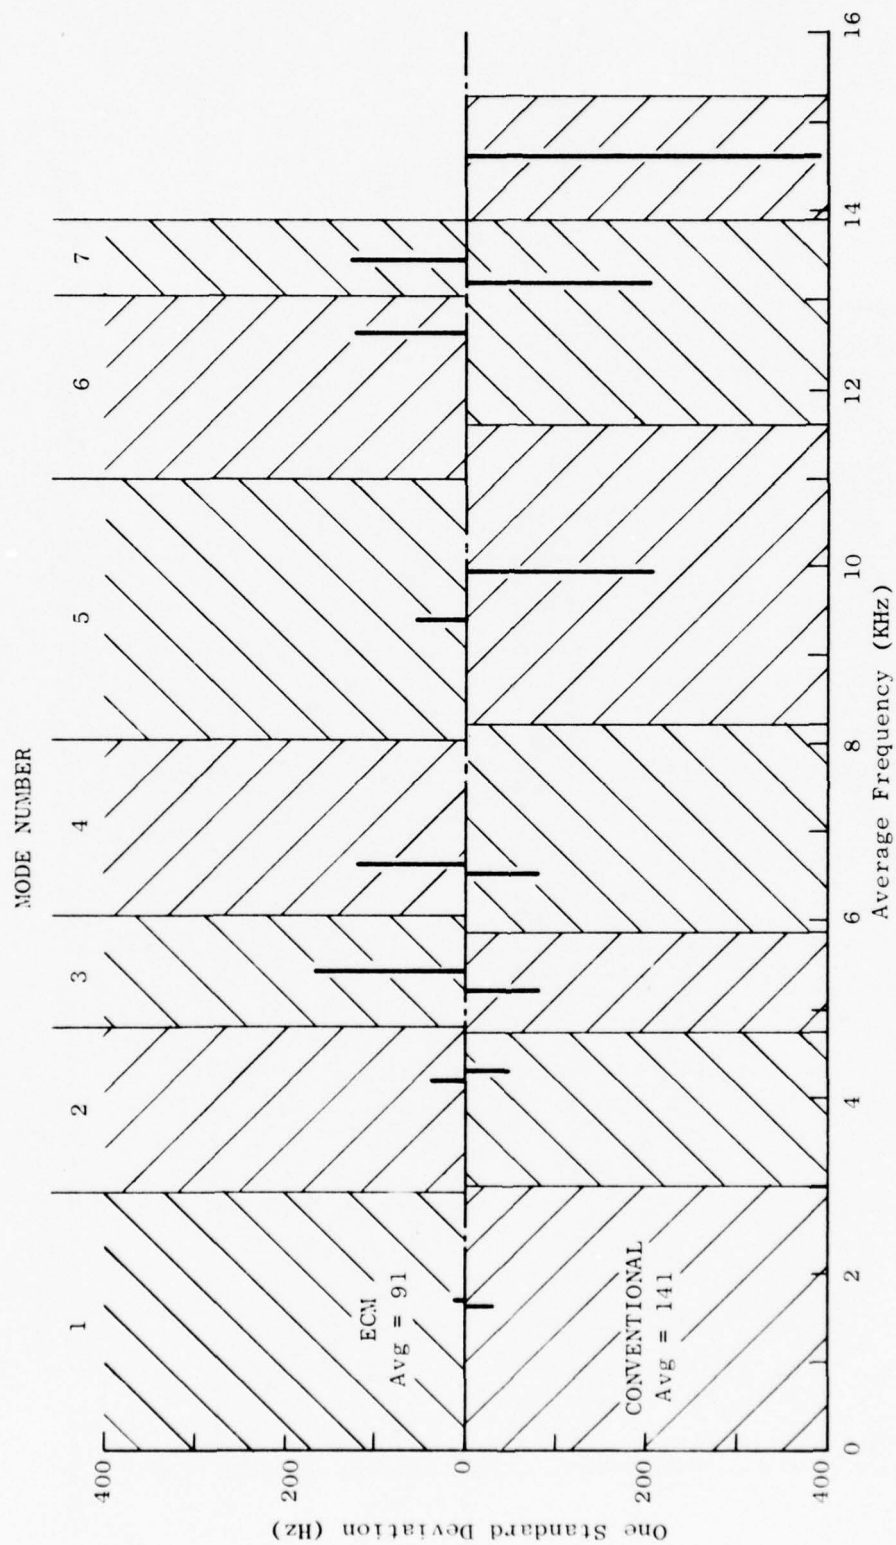


Figure 6. Resonant Frequency Summary, Stage 5 (Part No. 4013148-505P01), Standard Deviation Versus Average Frequency.



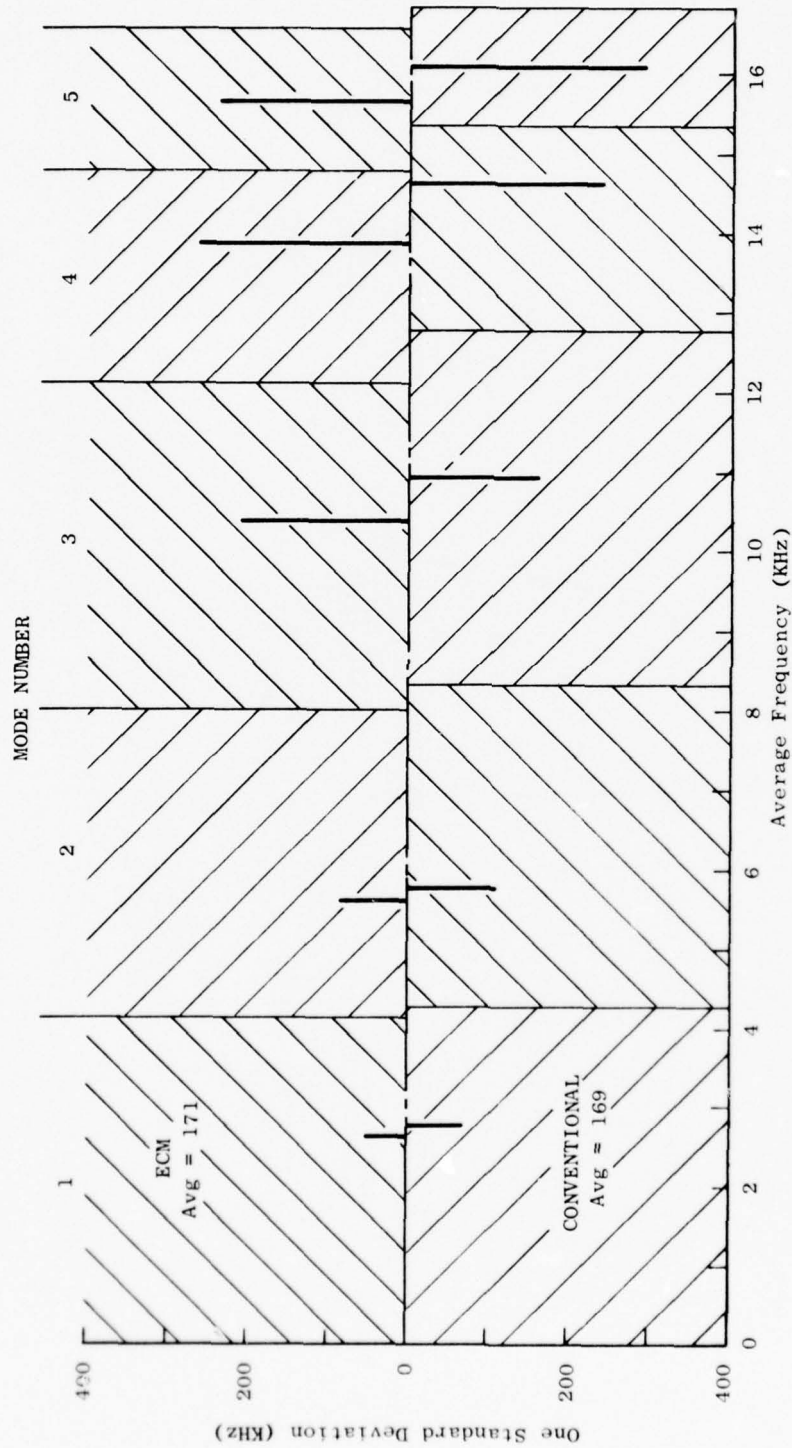



Figure 7. Resonant Frequency Summary, Stage 8 (Part No. 4013148-508P01), Standard Deviation Versus Average Frequency.

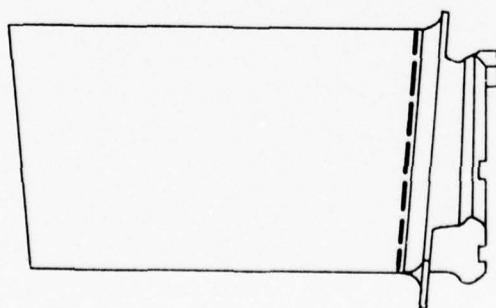

794 Hz  
Mode No. 4

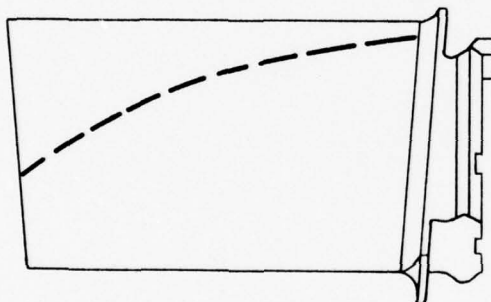


2534 Hz  
Mode No. 5

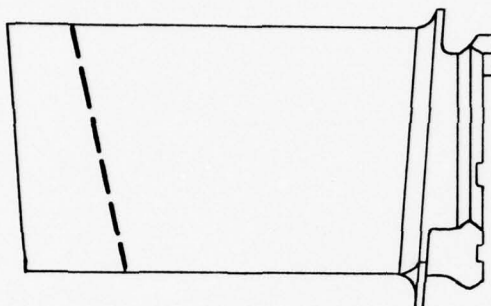


3370 Hz  
Mode No. 6


Figure 8. Resonant Frequencies and Nodal Patterns, Stage 2 Blade  
(Part No. 4013148-502P01), ECM Airfoil S/N 367.

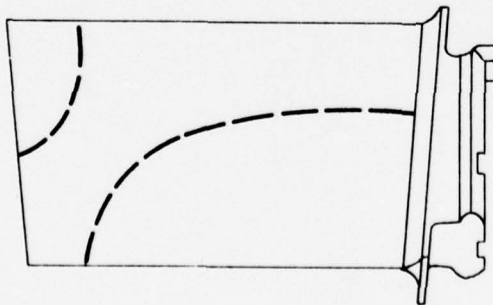

5554 Hz  
Mode No. 4

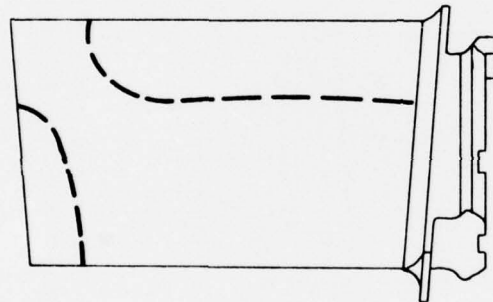


6320 Hz  
Mode No. 5

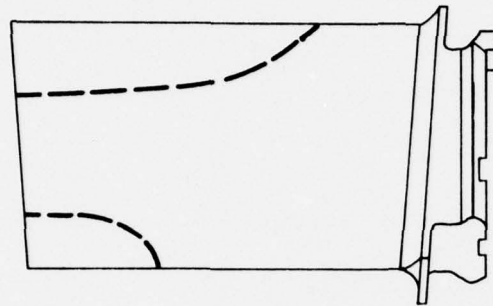


7480 Hz  
Mode No. 6


Figure 9. Resonant Frequencies and Nodal Patterns, Stage 2 Blade  
(Part No. 4013148-502P01), ECM Airfoil S/N 367.

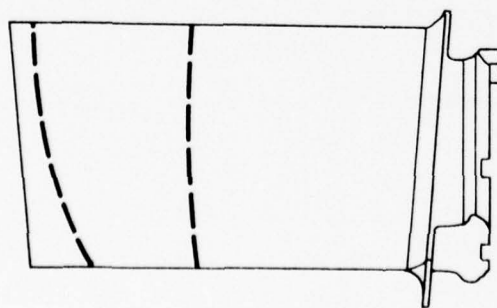

7916 Hz  
Mode No. 7

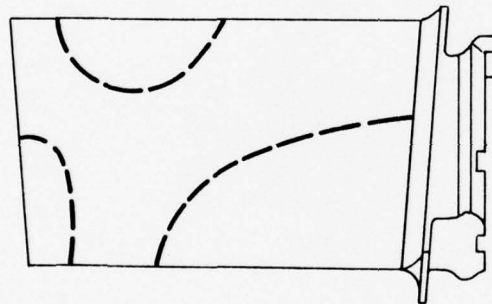


9849 Hz  
Mode No. 8

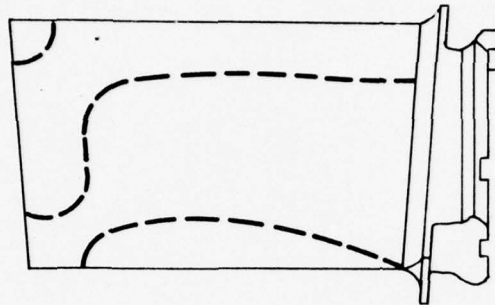


12,034 Hz  
Mode No. 9

Figure 10. Resonant Frequencies and Nodal Patterns, Stage 2 Blade  
(Part No. 4013148-502P01), ECM Airfoil S/N 367.

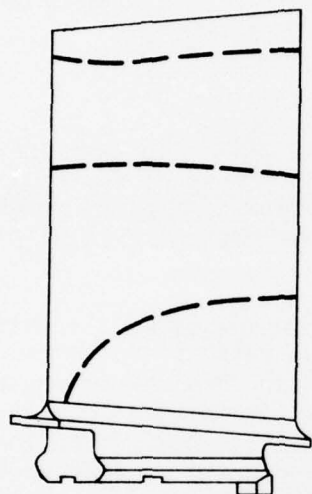

12,714 Hz  
Mode No. 10

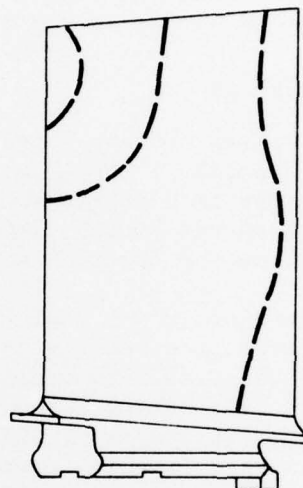

14,359 Hz  
Mode No. 11

Figure 11. Resonant Frequencies and Nodal Patterns,  
Stage 2 Blade (Part No. 4013148-502P01),  
ECM Airfoil S/N 367.

There does not appear to be a clear-cut advantage of ECM'd airfoils over airfoils produced by conventional means with regard to natural frequencies and nodal patterns. Stage 5, however, with its as-ECM's surfaces, does exhibit consistently better frequency scatter and standard deviation. The variability produced by hand rework on Stages 2 and 8 may have distorted similar results.

Location of the nodal lines, which relates to strain distribution, did not show more consistency in one type than in the other.

### C. Fatigue Results

One quarter set of each stage and manufacturer (the same ones used for frequencies and nodal patterns) were failed in the first flexural mode. Parts were clamped in fixtures to simulate engine fixity and driven in resonance using an air siren. Reference strain gages were applied to the parts to determine the level of stress.

The standard staircase fatigue test method was used. In this procedure, an arbitrary level of stress is estimated that will produce failure of the part in less than 10,000,000 cycles. If failure does not occur, the stress level is raised by a predetermined increment. The test is then conducted again on a different specimen, and the process is repeated until a failure does occur. After a failure occurs, the stress level is reduced by an increment and the test is repeated. If a failure occurs the stress is reduced for the next specimen while, if a failure does not occur the stress is increased and so on until a predetermined number of specimens is used up.

The fatigue results are presented in Figures 12 through 19. The data were analyzed using GE Specification E50TF39 entitled "Fatigue Testing - Compressor Blades and Vanes and Turbine Blades."

An advantage of ECM blades over conventional blades was found in regard to fatigue strength. The standard deviation of the ECM blades tended to be smaller than that for conventionally made blades. Hence, the average fatigue strength was diminished less for as-ECM'd blades than for conventional blades for a given design allowable strength.

Fatigue testing of the present lot of Stage 5 ECM blades showed an expectedly low fatigue strength in the unpeened condition. A comparison of blade and test specimen fatigue strength levels is contained in Table 1. Had a larger blade lot been available to provide a meaningful statistical basis, peened versus unpeened airfoils would have been tested. From test comparisons in previous studies however, a significant strength improvement resulted from peening.

This study successfully demonstrated production of high quality as-ECM R95 blades. As-peened fatigue strength comparisons between conventional machining and ECM show equal or superior values for the ECM-processed material.

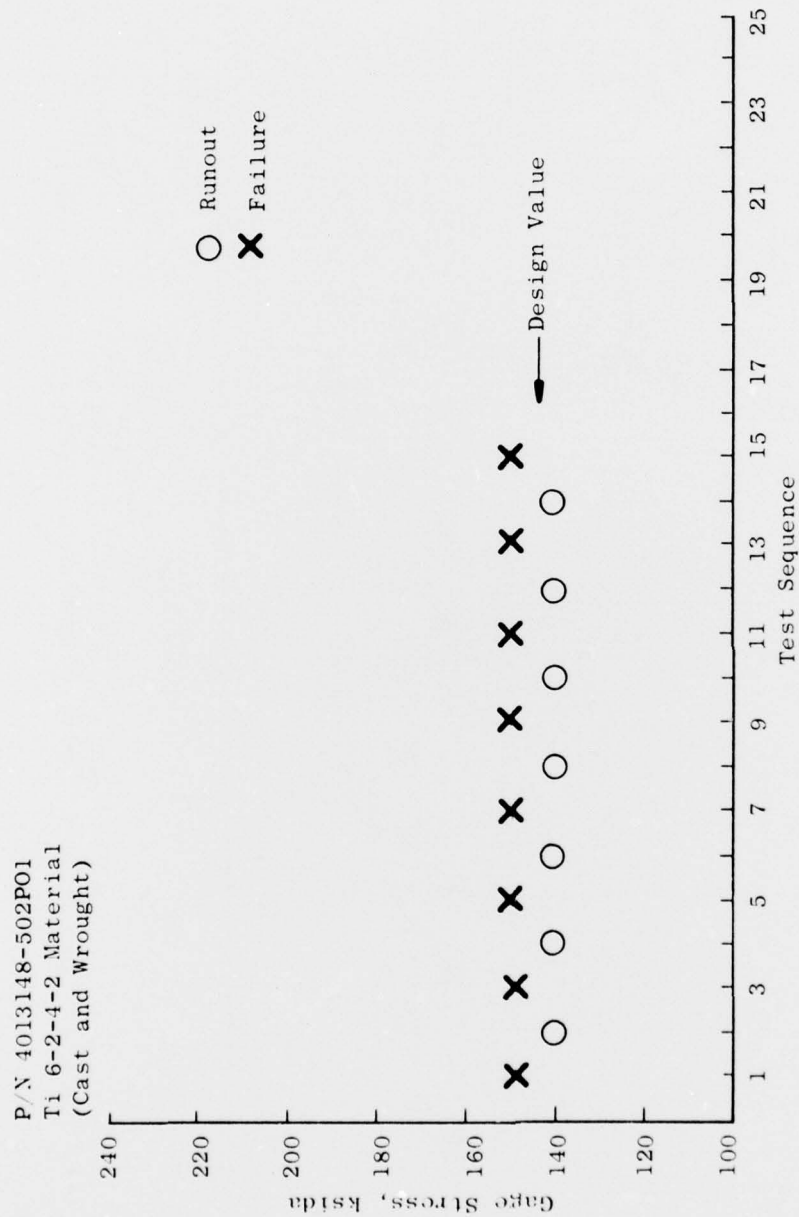


Figure 12. Fatigue Results, Stage 2 ECM Airfoil (Peened 6-10N).

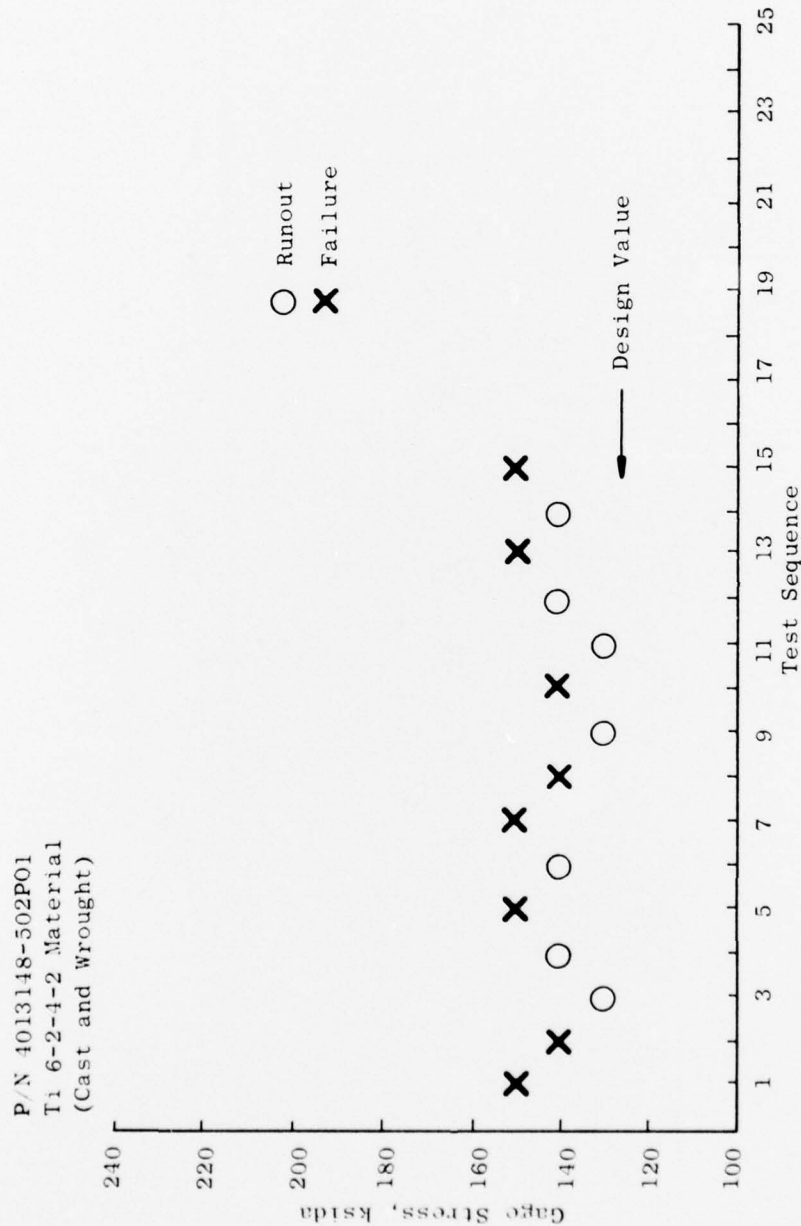


Figure 13. Fatigue Results, Stage 2 Conventional Airfoil (Peened 6-10N).

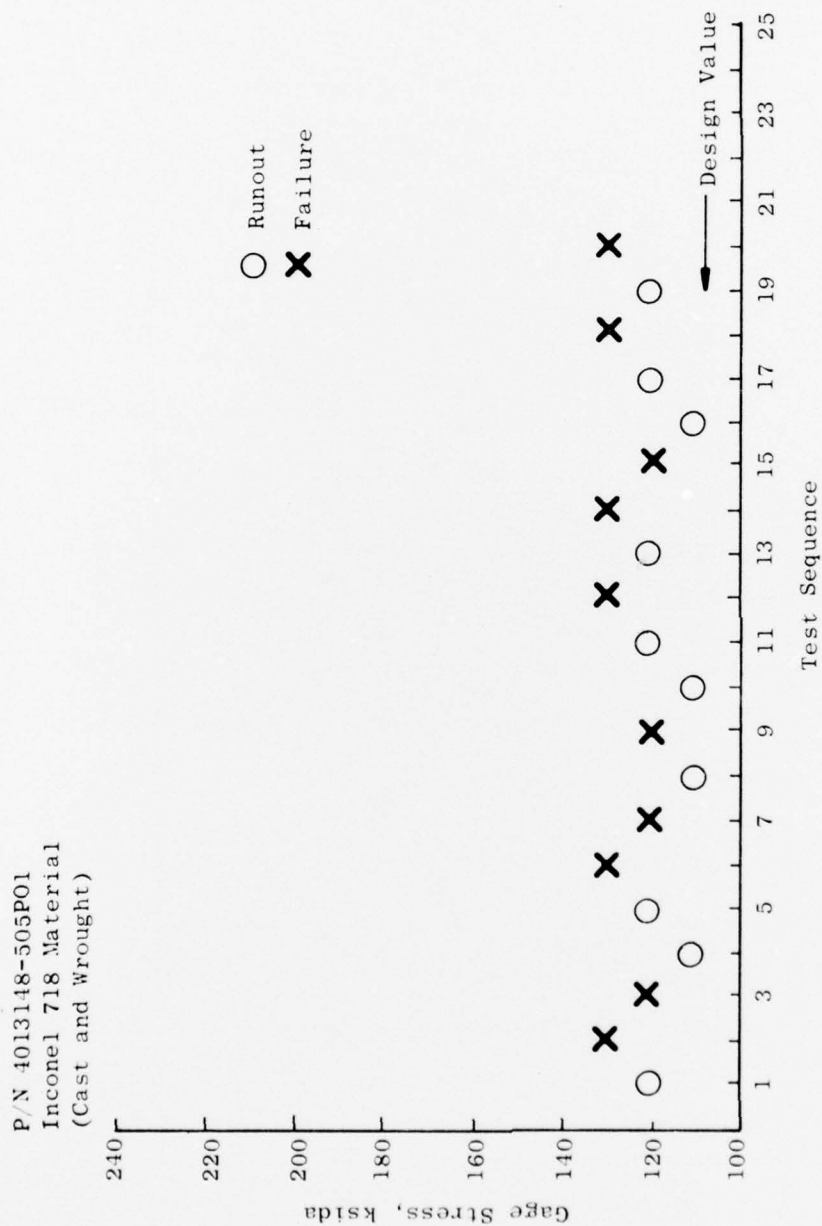


Figure 14. Fatigue Results, Stage 5 ECM Airfoil (Unpeened).

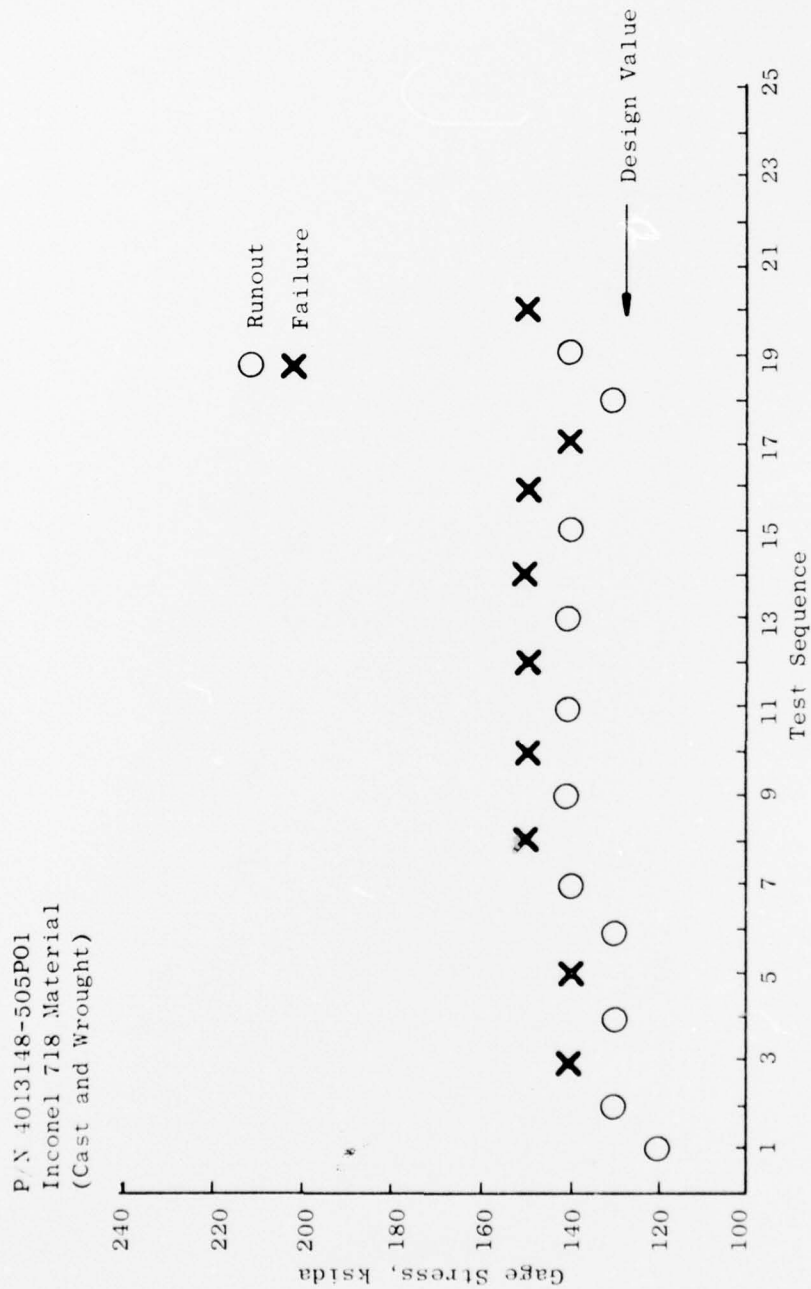


Figure 15. Fatigue Results, Stage 5 Conventional Airfoil (Peened 6-10N).

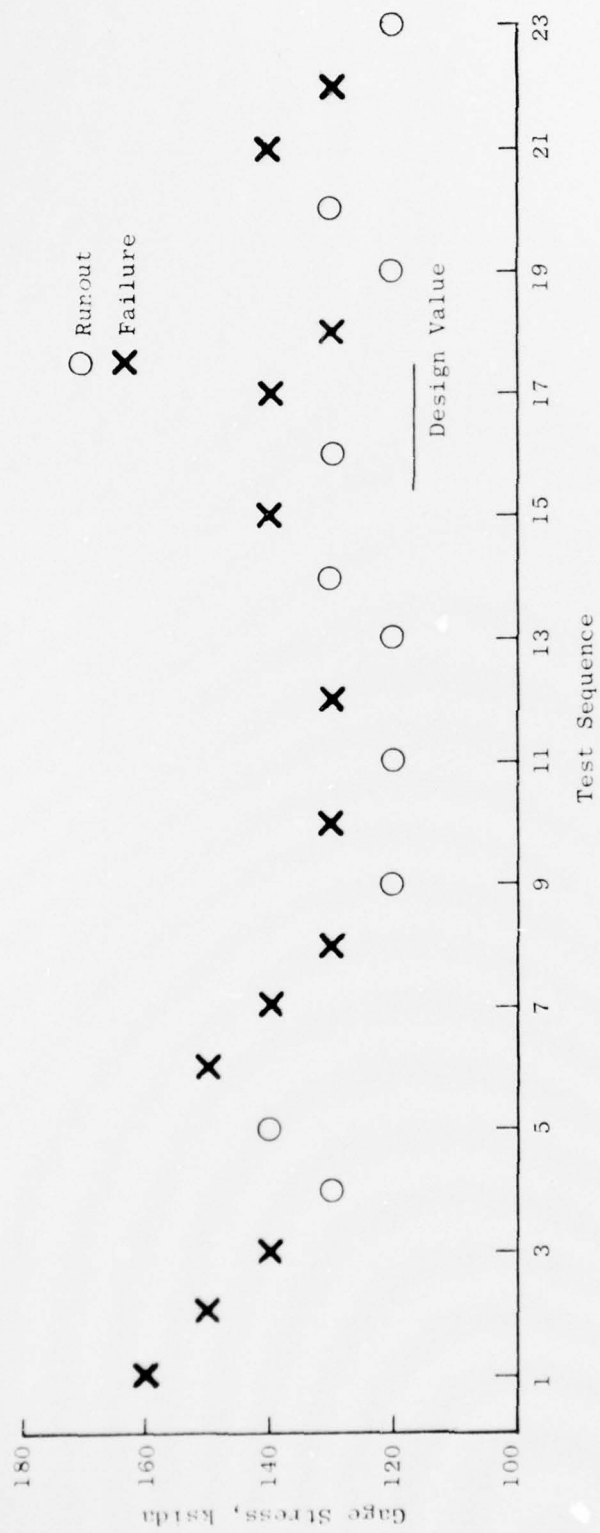


Figure 16. Fatigue Results, Stage 5 PM R95 ECM Airfoil (Unpeened).

P/N 4013148-508P01  
René 95 Material  
(Powdered)

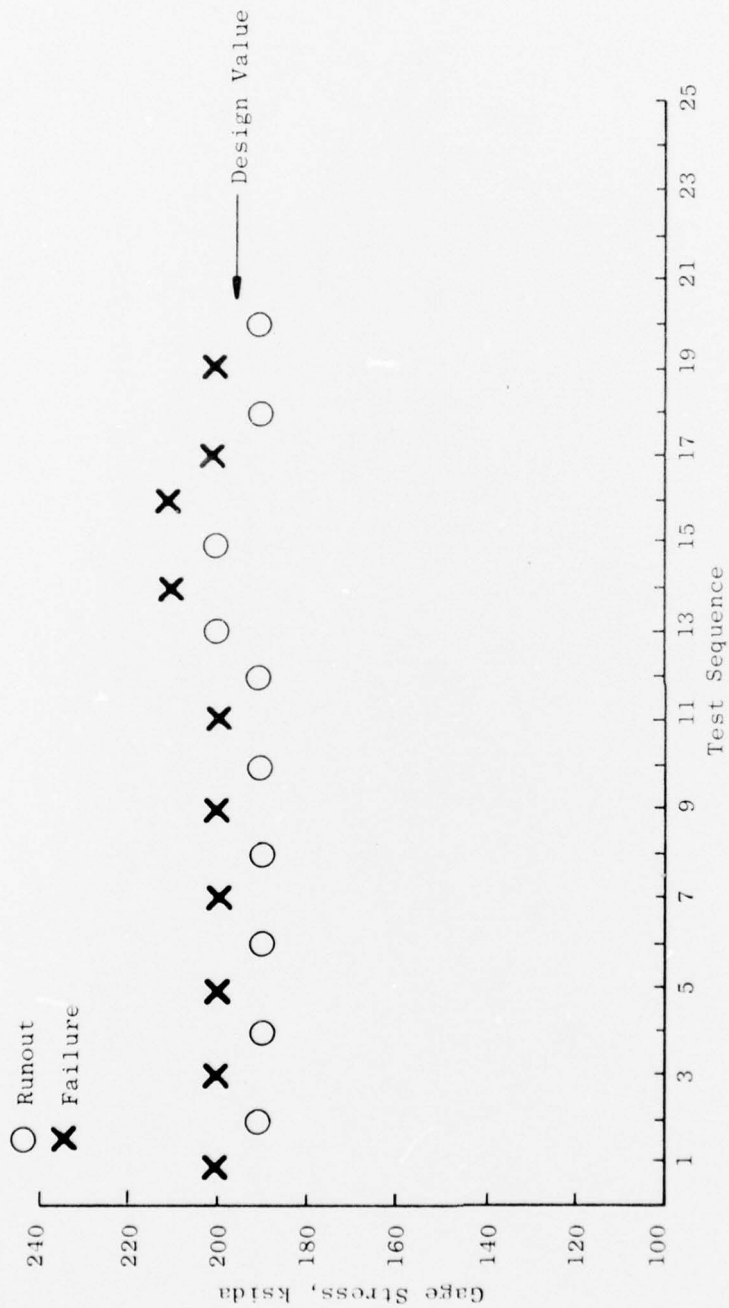


Figure 17. Fatigue Results, Stage 8 ECM Airfoil (Peened 6-10N).

P/N 4013148-508P01)  
 René 95 Material  
 (Cast and Wrought)

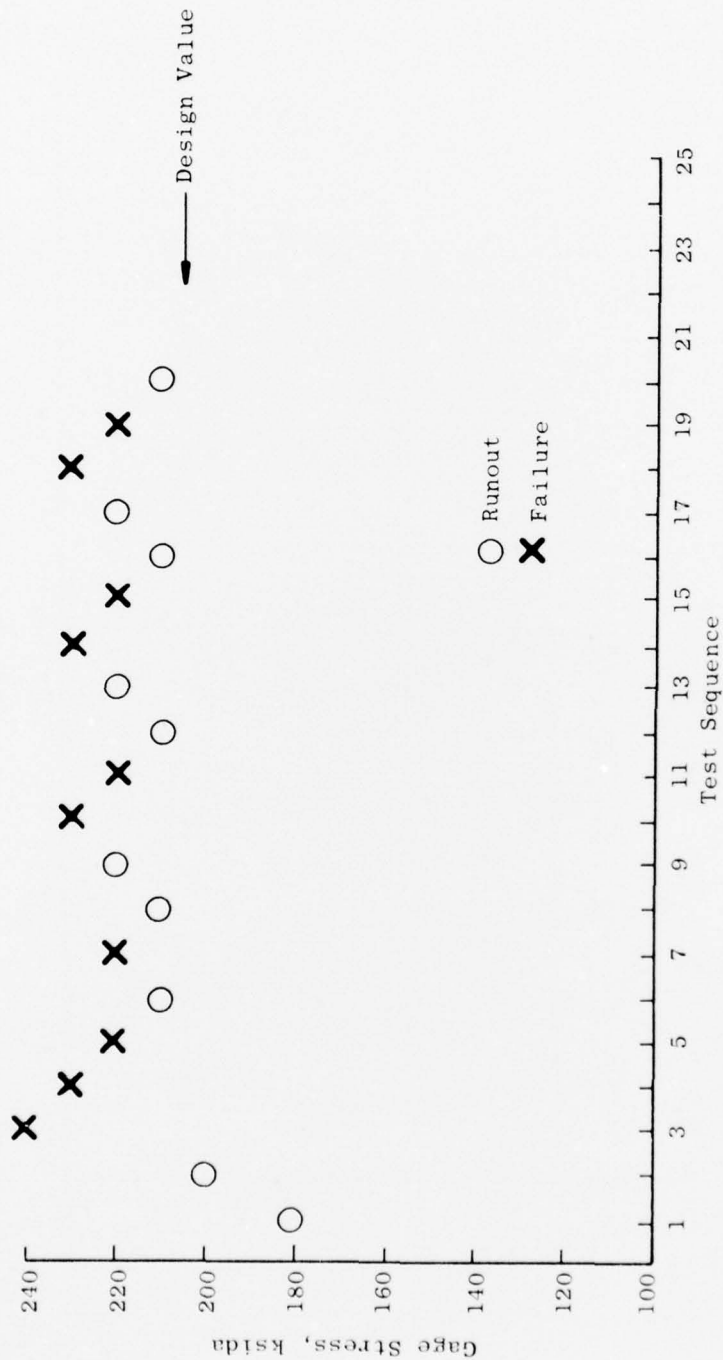


Figure 18. Fatigue Results, Stage 8 Conventional Airfoil (Peened 6-10N).

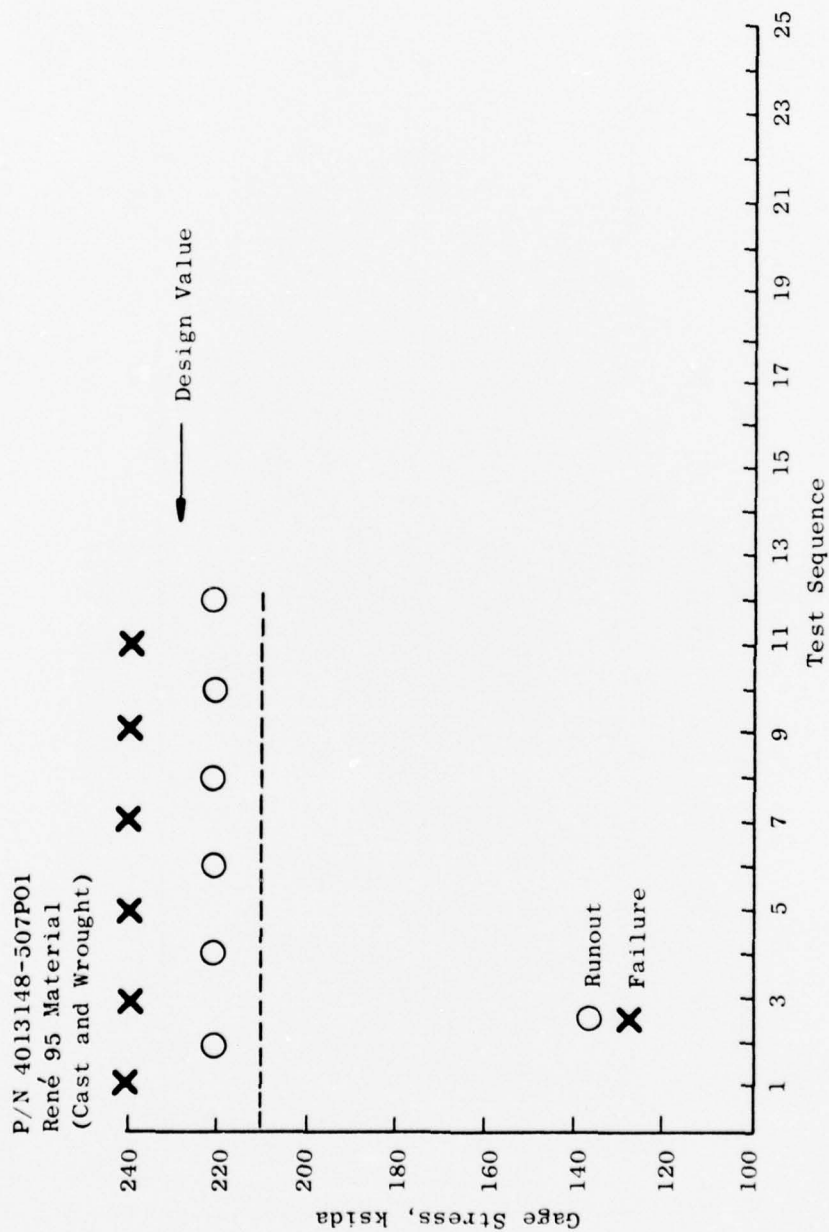


Figure 19. Fatigue Results, Stages 7 and 8 ECM Airfoil (Peened 6-10N).

The combination of good fatigue strength, dimensional and contour consistency and projected unit cost make the ECM blade production technique attractive for production of high strength nickel base alloy blades.

Estimates of the effects on compressor efficiency of the improved surface finish for all stages of a typical advanced compressor yield an improvement of 0.55%. The thicker hubs decrease this improvement by 0.1% yielding a net improvement in compressor efficiency of 0.45%.

AS-HIP'd powder metal (PM) René 95 does not have the base fatigue strength of cast and wrought material, as is evident from the lower strength of the René 95 stage 8 blades in Figure 17. A previous study produced ECM blades for Stage 8 using René 95 cast and wrought material; partial results from this prior study are presented in Figure 19, where fatigue strength is higher than that of the conventional blades (Figure 18). To this comparison must be added the knowledge that the cast and wrought René 95 used was better than the minimum specification and that the PM René 95 process is still being refined. The achievement of equal material strength is important, since René 95 blades are economical only if PM preforms can be made.

## SECTION V

### PROCESS STATUS

No attempt was made during the major part of the ECM study to optimize the manufacturing sequence to be cost effective. The program concentrated on the production of a high quality airfoil and, therefore, machined the dovetail last because of concern that the completed dovetail would be damaged when it carried the high current involved in the ECM generation of the airfoil. The first phase successfully produced high quality airfoils in three different sizes and materials as is evident from the results presented in Section IV "Testing and Inspection". The airfoil-making part of the ECM process was well in hand for a production-oriented process.

From the experience of the first phase of work it was apparent that the processing sequence needed to be changed to make the ECM manufacture process cost competitive for high temperature materials. Five items were noted as areas requiring improvement:

- 1) Quality of raw material
- 2) Machining of blanks to prepare for ECM
- 3) The removal of excess material below the platform
- 4) The finish machining of the dovetail pressure face
- 5) The need to complete all machining of the dovetail and platform underside prior to generation of the airfoil to free the airfoil of fatigue stresses induced while holding the airfoil to machine the dovetail in the original process.

A review was made of these five items and the first four were believed within current state-of-the art capability for high production manufacturing and, therefore, not in need of further study. The fifth item presented a specific problem involved with the limited dovetail shank size available. Further, problems of reliably sealing a charged electrode during the ECM process from the shank area were believed to provide a further barrier.

Difficulty with the powder metal material involved in the stage 8 ECM blades left the program technically successful but with a shortfall of 42 blades. The funding involved in the Stage 8 blade shortfall was diverted to the task of removing questions about the manufacturing sequence by producing a lot of approximately 30 Stage-5 blades using the remaining R95 material. This lot of blades would be made dovetail first.

The work of producing a lot of 30 airfoils was to be done at Lehr Precision, the vendor where the Stage 5 blades were made by ECM from Inconel 718 material during the original phase of the program. Several approaches


were studied for the dovetail-first manufacture process. A metal matrix cast around the finished dovetail provided a piece for the ECM process which directly resembled the blank before the dovetail was machined. This arrangement isolated the dovetail from the charged electrolyte and provided a sufficient cross section for the high current of the ECM blade processing. The arrangement also provided reliable fixturing surfaces for both the ECM process and the subsequent grinding operations which were needed to finish the four sides of the blade platform.

The equipment involved is illustrated in Figure 20. The details of the dovetail-first manufacture process were developed during a four blade pilot run and were then successfully applied to produce a lot of twenty-six high quality Stage 5 airfoils.


As a result of the work accomplished on the final phase of the program, it was concluded that ECM Blades can be produced with a high level of consistency of the product when compared to the present experience in conventional blade machining techniques. The end product has only the material variance and process tolerance effect to consider in blade life predictions, since there is no physical work applied to the material in the process and the end product is unaffected by the variations of tool and abrasive benching abuses inherent in conventional blade manufacture.

With proper process considerations, an ECM produced blade was judged cost competitive with a conventionally machined blade. It was estimated that, with such materials as R95, the ECM blade could be produced for the same price as an Inconel 718 blade. Blades made by conventional machining were estimated to cost nearly twice as much as Inconel 718 blades.


View of Controls  
for ECM Equipment

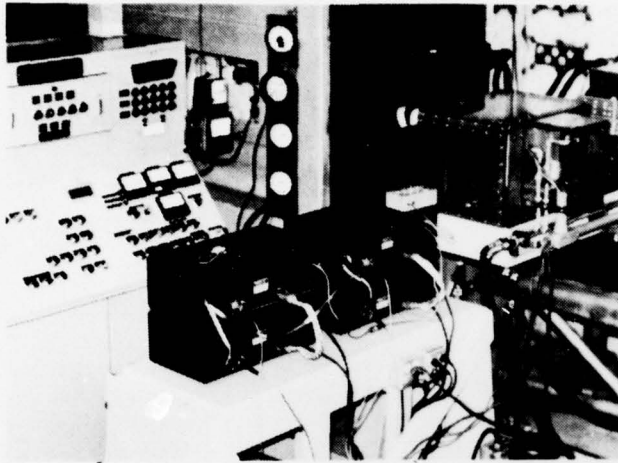

Closeup of Partically Completed  
Blade in ECM Setup

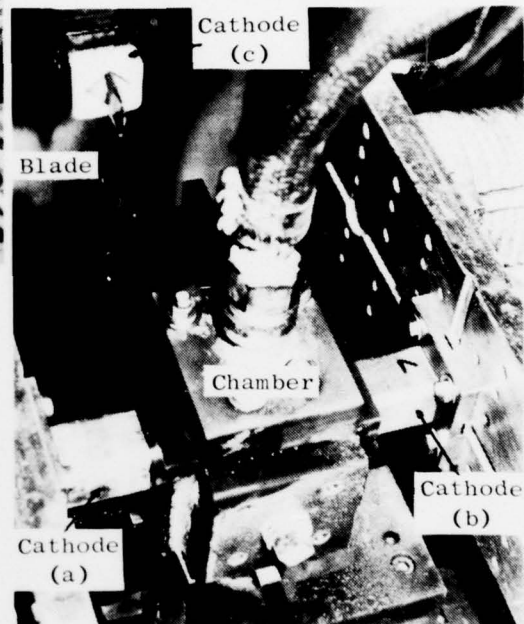

Stage 5 R95 Blade At Various  
Points in the ECM Process

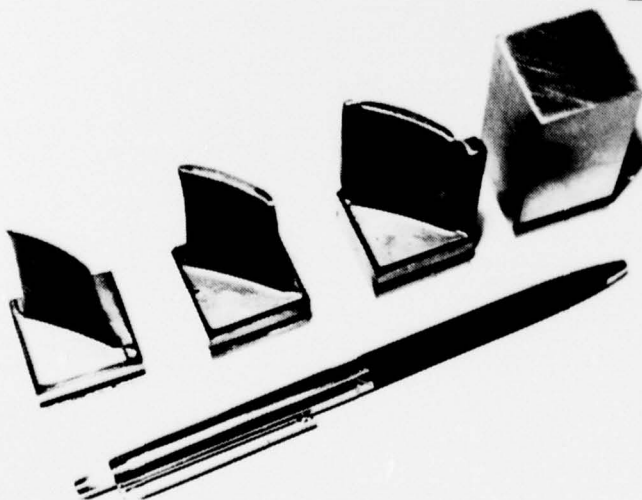

(a), (b) and (c)  
are the Three  
Moving Electrodes

Figure 20. ECM Final Process.