

DDC/TISIR

HEADQUARTERS

OGDEN AIR LOGISTICS CENTER

UNITED STATES AIR FORCE

HILL AIR FORCE BASE, UTAH 84406

AD A 052698

AD NO. 1
DDC FILE COPY

⑥ SURVEILLANCE REPORT

STAGE I

DISSECTED MOTORS

PHASE IX

PROPELLANT AND COMPONENT TESTING

⑨ Quarterly Rept.

PROPELLANT LAB SECTION

⑩ John A. Thompson

MANCP-10000-100
392(78) move

COPY AVAILABLE TO DDC DOES NOT
PERMIT FULLY LEGIBLE PRODUCTION

⑪ MAR 1978

⑫ 96p.

DDC

APR 14 1978

APPROVED FOR PUBLIC RELEASE, DISTRIBUTION UNLIMITED

407387

YB

SURVEILLANCE QUARTERLY REPORT

STAGE I DISSECTED MOTORS

PHASE IX PROPELLANT & COMPONENT TESTING

Author

John A. Thompson
JOHN A. THOMPSON, Chemist
Component & Combustion Test Unit

Engineering & Statistical Review By

John K. Scambia
JOHN K. SCAMBIA, Project Engineer
Service Engineering

Edward J. Erickson
EDWARD J. ERICKSON, Statistician
Data Analysis Unit

Recommended Approval By

Ronald F. Larsen
RONALD F. LARSEN, Chief
Physical & Mechanical Test Unit

Leonidas A. Brown
LEONIDAS A. BROWN, Chief
Component & Combustion Test Unit

Approved By

Don F. Woods
DON F. WOODS, Chief
Propellant Laboratory Section

March 1978

Industrial Products & Ldg Gear Division
Directorate of Maintenance
Ogden Air Logistics Center
United States Air Force
Hill Air Force Base, Utah 84406

HO 2633

UP

ABSTRACT

Testing was performed to determine the useful shelf/service life for LGM-30 Stage I Rocket Motors. A three year storage program for propellant and components was started in May 1961. This program was then extended to a ten year study and later continued indefinitely to assure that a deterioration in motor physical characteristics could be detected in time to take some corrective actions before the weapon system performance deteriorated below an acceptable level.

This report covers only propellant data and limited case bond data. The malfunction of an environmental chamber destroyed component samples that had originally been part of this testing program (and the inadvertent burning of some motors during dissection reduced the material available for testing). Planned dissection of selected motors in the future will provide samples for continued component testing. Test specimens for this reporting period were obtained from motors STM-012, 0012099, 0012199 and UP7775 block propellant.

Separate analyses were made on the respective motors and block propellant for the first time in this report and are shown in the regressions. The plotting symbols for each motor and block propellant are listed in the statistical analyses section.

The data from this test period was combined with data from previous testing and entered into the G085 computer for storage, analysis, and regression analysis. From the statistical analysis of all data tested to date, significant degradation of the propellant does not appear likely for at least two years past the oldest data point.

Future testing will be conducted on dissected motors.

100	☒
102	☐
104	☐
106	☐
108	☐
110	☐
112	☐
114	☐
116	☐
118	☐
120	☐
122	☐
124	☐
126	☐
128	☐
130	☐
132	☐
134	☐
136	☐
138	☐
140	☐
142	☐
144	☐
146	☐
148	☐
150	☐
152	☐
154	☐
156	☐
158	☐
160	☐
162	☐
164	☐
166	☐
168	☐
170	☐
172	☐
174	☐
176	☐
178	☐
180	☐
182	☐
184	☐
186	☐
188	☐
190	☐
192	☐
194	☐
196	☐
198	☐
200	☐
202	☐
204	☐
206	☐
208	☐
210	☐
212	☐
214	☐
216	☐
218	☐
220	☐
222	☐
224	☐
226	☐
228	☐
230	☐
232	☐
234	☐
236	☐
238	☐
240	☐
242	☐
244	☐
246	☐
248	☐
250	☐
252	☐
254	☐
256	☐
258	☐
260	☐
262	☐
264	☐
266	☐
268	☐
270	☐
272	☐
274	☐
276	☐
278	☐
280	☐
282	☐
284	☐
286	☐
288	☐
290	☐
292	☐
294	☐
296	☐
298	☐
300	☐
302	☐
304	☐
306	☐
308	☐
310	☐
312	☐
314	☐
316	☐
318	☐
320	☐
322	☐
324	☐
326	☐
328	☐
330	☐
332	☐
334	☐
336	☐
338	☐
340	☐
342	☐
344	☐
346	☐
348	☐
350	☐
352	☐
354	☐
356	☐
358	☐
360	☐
362	☐
364	☐
366	☐
368	☐
370	☐
372	☐
374	☐
376	☐
378	☐
380	☐
382	☐
384	☐
386	☐
388	☐
390	☐
392	☐
394	☐
396	☐
398	☐
400	☐
402	☐
404	☐
406	☐
408	☐
410	☐
412	☐
414	☐
416	☐
418	☐
420	☐
422	☐
424	☐
426	☐
428	☐
430	☐
432	☐
434	☐
436	☐
438	☐
440	☐
442	☐
444	☐
446	☐
448	☐
450	☐
452	☐
454	☐
456	☐
458	☐
460	☐
462	☐
464	☐
466	☐
468	☐
470	☐
472	☐
474	☐
476	☐
478	☐
480	☐
482	☐
484	☐
486	☐
488	☐
490	☐
492	☐
494	☐
496	☐
498	☐
500	☐
502	☐
504	☐
506	☐
508	☐
510	☐
512	☐
514	☐
516	☐
518	☐
520	☐
522	☐
524	☐
526	☐
528	☐
530	☐
532	☐
534	☐
536	☐
538	☐
540	☐
542	☐
544	☐
546	☐
548	☐
550	☐
552	☐
554	☐
556	☐
558	☐
560	☐
562	☐
564	☐
566	☐
568	☐
570	☐
572	☐
574	☐
576	☐
578	☐
580	☐
582	☐
584	☐
586	☐
588	☐
590	☐
592	☐
594	☐
596	☐
598	☐
600	☐
602	☐
604	☐
606	☐
608	☐
610	☐
612	☐
614	☐
616	☐
618	☐
620	☐
622	☐
624	☐
626	☐
628	☐
630	☐
632	☐
634	☐
636	☐
638	☐
640	☐
642	☐
644	☐
646	☐
648	☐
650	☐
652	☐
654	☐
656	☐
658	☐
660	☐
662	☐
664	☐
666	☐
668	☐
670	☐
672	☐
674	☐
676	☐
678	☐
680	☐
682	☐
684	☐
686	☐
688	☐
690	☐
692	☐
694	☐
696	☐
698	☐
700	☐
702	☐
704	☐
706	☐
708	☐
710	☐
712	☐
714	☐
716	☐
718	☐
720	☐
722	☐
724	☐
726	☐
728	☐
730	☐
732	☐
734	☐
736	☐
738	☐
740	☐
742	☐
744	☐
746	☐
748	☐
750	☐
752	☐
754	☐
756	☐
758	☐
760	☐
762	☐
764	☐
766	☐
768	☐
770	☐
772	☐
774	☐
776	☐
778	☐
780	☐
782	☐
784	☐
786	☐
788	☐
790	☐
792	☐
794	☐
796	☐
798	☐
800	☐
802	☐
804	☐
806	☐
808	☐
810	☐
812	☐
814	☐
816	☐
818	☐
820	☐
822	☐
824	☐
826	☐
828	☐
830	☐
832	☐
834	☐
836	☐
838	☐
840	☐
842	☐
844	☐
846	☐
848	☐
850	☐
852	☐
854	☐
856	☐
858	☐
860	☐
862	☐
864	☐
866	☐
868	☐
870	☐
872	☐
874	☐
876	☐
878	☐
880	☐
882	☐
884	☐
886	☐
888	☐
890	☐
892	☐
894	☐
896	☐
898	☐
900	☐
902	☐
904	☐
906	☐
908	☐
910	☐
912	☐
914	☐
916	☐
918	☐
920	☐
922	☐
924	☐
926	☐
928	☐
930	☐
932	☐
934	☐
936	☐
938	☐
940	☐
942	☐
944	☐
946	☐
948	☐
950	☐
952	☐
954	☐
956	☐
958	☐
960	☐
962	☐
964	☐
966	☐
968	☐
970	☐
972	☐
974	☐
976	☐
978	☐
980	☐
982	☐
984	☐
986	☐
988	☐
990	☐
992	☐
994	☐
996	☐
998	☐
1000	☐

TABLE OF CONTENTS

	<u>Page</u>
Abstract	ii
List of Figures	iv
Glossary of Terms and Abbreviations	vii
Introduction	1
Table 1, Test Program	3
Statistical Approach	5
Test Results	7
Conclusions	10
Recommendations	11
Distribution List	86
DD1473	87

LIST OF FIGURES

<u>Figure Nr</u>		<u>Page</u>
Regression Plot, Low Rate Tensile, 2 in/min		
1	Strain at Maximum Stress	13
2	Maximum Stress	14
3	Strain at Rupture	15
4	Stress at Rupture	16
5	Modulus	18
Regression Plot, Low Rate Tensile, 20 in/min		
6	Strain at Maximum Stress	20
7	Maximum Stress	21
8	Strain at Rupture	22
9	Stress at Rupture	23
10	Modulus	25
Regression Plot, High Rate Tensile		
11	Strain at Maximum Stress	27
12	Maximum Stress	28
13	Strain at Rupture	29
14	Stress at Rupture	30
15	Modulus	31
Regression Plot, High Rate Triaxial Tensile, 600 psi		
16	Strain at Maximum Stress	33
17	Maximum Stress	34
18	Strain at Rupture	35

LIST OF FIGURES (CONT.)

<u>Figure Nr</u>		<u>Page</u>
19	Stress at Rupture	36
20	Modulus	37
21	Regression Plot, Casebond Tensile	39
	Regression Plot, Creep, 10 lb load	
22	Compliance at 10 sec	41
23	Compliance at 20 sec	42
24	Compliance at 1000 sec	43
25	Compliance at 10,000 sec	45
	Regression Plot, Creep, 12 lb load	
26	Compliance at 10 sec	47
27	Compliance at 20 sec	48
28	Compliance at 1,000 sec	49
29	% Strain at Rupture	51
	Regression Plot, Stress Relaxation 3% Strain	
30	Modulus at 10 sec	53
31	Modulus at 50 sec	54
32	Modulus at 100 sec	55
33	Modulus at 1,000 sec	56
	Regression Plot, Stress Relaxation 5% Strain	
34	Modulus at 10 sec	58
35	Modulus at 50 sec	59
36	Modulus at 100 sec	60
37	Modulus at 1000 sec	61

LIST OF FIGURES (CONT)

<u>Figure Nr</u>		<u>Page</u>
38	Regression Plot, Constant Strain	63
39	Regression Plot, Hardness, Shore A, 10 sec	65
40	Regression Plot, Burn Rate, 500 psi	67
41	Regression Plot, Burn Rate, 1000 psi	69
42	Regression Plot, Heat of Explosion	71
43	Regression Plot, Ignitability	73
	Regression Plot, Differential Thermal Analysis, 12°C rise/min	
44	Endotherm 1	75
45	Exotherm 1	76
46	Ignition Temperature	78
	Regression Plot, Sol Gel	
47	Percent Extractables	80
48	Gel Swell Ratio	81
49	Density	82
50	Crosslink Density	83
	Failure Envelopes	
51	STM-012	84
52	Motor S/N 0012199	85

GLOSSARY OF TERMS AND ABBREVIATIONS

Aging Trend	A change in properties or performance resulting from aging of material or component
CSA	Cross Sectional Area
DB	Dogbone
Degradation	Gradual deterioration of properties or performance
E	Modulus (psi), defined as stress divided by strain along the initial linear portion of the curve.
EB	End Bonded
EGL	Effective Gage Length
em	Strain at maximum stress
er	Strain at rupture
"F" ratio	The ratio of the variance accounted for by the regression function to the random unexplained variance. The regression function having the most significant "F" ratio is used for plotting data. The ratio is also used in detecting significant changes in random variation between succeeding time points
JANNAF	Joint Army, Navy, NASA, Air Force Committee
MANCP	Propellant Lab Section at Ogden Air Logistics Center
Ogden ALC	Ogden Air Logistics Center, Air Force Logistics Command
r or R	The Correlation Coefficient is a measure of the degree of closeness of the linear relationship between two variables
Regression Equation	The general form of the regression equation is $Y = a + bx$
Regression Line	Line representing mean test values with respect to time
S_b	Standard error of estimate of the regression coefficient

GLOSSARY OF TERMS AND ABBREVIATIONS (cont)

S_e or $S_{y.x}$	Standard deviation of the data about the regression line
S_m	Maximum Stress
S_r	Stress at rupture
Standard Deviation (S_y)	Square root of variance
Strain Rate	Crosshead speed divided by the EGL
"t" test	A statistical test used to detect significant differences between a measured parameter and an expected value of the parameter (determines if regression slope differs from zero at the 95% confidence level)
Variance	The sum of squares of deviations of the test results from the mean of the series after division by one less than the total number of test results
3 Sigma Band	The area between the upper and lower 3 sigma limit. It can be expected that 99.73% of the inventory represented by the test samples would fall within this range assuming that the population is normally distributed.
90-90 Band	It can be stated with 90% confidence that 90% of the inventory represented by the test samples would fall within this range assuming that the population is normally distributed

INTRODUCTION

A. PURPOSE:

This report contains test data from samples of LGM-30 Stage I, Wings I-V TP-H1011 propellant and case bond specimens. Testing was performed by the Propellant Laboratory Section (MANCP) for the Engineering and Reliability Branch of the Airmunitions Management Division (MMWRM) under Project M82934C-WNL17514. This report is the ninth in this series. Data from this test period and propellant test data from the eight previous reports were entered into the G085 computer for regression analysis. The regressions are shown in this report.

B. TEST PROGRAM:

The LGM-30 Laboratory and Component Program includes the testing of materials used in the main case, aft closure, ignition assemblies, and main grain propellant. This report covers TP-H1011 propellant and case bond specimens. Table I outlines the test program.

Propellant for testing was obtained from three dissected motors, STM-012, a motor prepared by Thiokol specifically for dissection, S/N 0012099, A SLIM motor, and motor S/N 0012199 selected from the inventory for dissection and UP-7775 block propellant.

C. HISTORICAL BACKGROUND:

In May 1961, Thiokol began a three year LGM-30 laboratory storage and test program to determine the rate of degradation with age for Stage I materials. During June 1962 and again in August 1963, additional samples were included. New samples were added in July and August 1964 when the

surveillance testing program was extended to ten years (Test Plan 0717-62-0967, 53-8). Carton block propellant, batch UP-7775, containing TP-H1011 propellant cast in March 1962 was added to the program in 1964.

Samples added to the inventory in 1964 were considered to be a new population, but were combined in regression analysis with the three dissected motors. The history of testing of these materials is found in MQQP Report Nrs. 109A(67), 144(68), 208(71) and 358(76). Physical transfer of the specimens from Thiokol to Ogden ALC was made in June 1967.

TABLE I

TEST PROGRAM

All Temperatures in Fahrenheit

STM-012, SN 0012099, SN 0012199, UP-7775

<u>Test</u>	<u>Conditions</u>	<u>Spec/ Cond</u>	<u>Spec Conf</u>
Tensile	77°, 2.0 & 20 in/min	5 ea	JANNAF Dogbone
Creep	77°, 10 & 12 lb load	3 ea	JANNAF Dogbone
Stress Relax	77°, 3 & 5% strain	3 ea	1/2" x 1/2" x 4"
Strain Dilatation	77°, .25 in/ in/min	3 ea	1/2" x 1/2" x 4"
Hardness	77°, initial 7 10 sec	5 ea	Dogbone Ends
HOE	77°	3 ea	1/2" x 3/8" x 1"
Burning Rate	77°, 500 & 1,000 psi	5 ea	.156" x .156" x 5"
DTA	77° start	3 ea	0.040" wafer
Ignitability	77°, 168 cal/ cm ² /sec	3 ea	0.050" wafer
Sol Gel	77°	6 ea	1/2" x 1/2" x 1/2"
UP-7775 will <u>NOT</u> be used on the following tests:			
High rate Tensile	77°, 1,000 in/in/min	5 ea	3/4" GL Dogbone
Triaxial High Rate	77°, 1,000 in/in/min 600 psi	3 ea	3/4" GL Rail
Dynamic Response	77°, 70 gm ct wt	3 ea	3.3" x .33" x 0.690" disc
Biaxial constant Strain	77°	3 ea	3/4" GL Rail

TABLE I (cont)

<u>Test</u>	<u>Conditions</u>	<u>Spec/Cond</u>	<u>Spec Conf</u>
Failure Envelope	Temp: -50° -20°, 10° 40°, 77° 130°, & 180°F at a rate of 0.2, 2.0, & 20 in/min	3 ea	JANNAF Dogbone
STM012 and 0012199 only will be for the following tests:			
Case Bond Tensile	77°, 0.2 in/ min	10 ea	1" x 5/8" x 3/4"
Tear Energy	77°F $\pm$ 2°	8ea	0.1" x 1.18" x 3"
Poisson's Ratio (Strain Dilatation) 10, 15, 20 25, 30%	77°F $\pm$ 2°	6 per/ condition	0.50" x 0.50" x 4"

STATISTICAL ANALYSIS

The objective of this statistical analysis is to determine whether or not any aging trends are demonstrated by accumulated test data in order to assist Service Engineering to more accurately predict motor serviceability.

Propellant was made available for testing and statistical analysis to obtain an overall view of the aging trends affecting the First Stage Dissected Motor Program. The sampling consists of data from two dissected operational motors (0012099 and 0012199), and carton propellant (batch UP-7775). One motor (STM-012) was prepared by Thiokol specifically for the dissection program.

A Multi-symbol Regression Analysis Program was used to determine aging trends. The sampling is combined for each test parameter in a single regression analysis. The linear equation ($Y = a + bX$) was found to be the best fit model for the data in this report. A composite population aging trend line is then calculated accepting the fact that individual aging of different populations may be masked.

The Multi-symbol Program uses a unique plotting code for each motor and carton data on the regression plots. This method of data plotting allows a visual display of the overall relationship between the various origins of data and how they relate to the overall least square aging trend line.

The regression program uses an analysis with individual data points from different time periods combined to establish a least squares aging trend line for the overall data. The variance about the regression line, obtained using individual values of the dependent variable, was used to compute a tolerance interval such that at the 90% confidence level 90% of the population falls within this interval. This tolerance interval was

extrapolated to a maximum of 24 months to give an indication of the statistical significance of the slope of any aging trends. The computer tolerance interval about the composite regression line is wider than what the tolerance interval would be about any individual motor or carton regression line because of the increased data spread introduced by combining different populations of data. The "t" values and the significance of this statistic, which are reported for each regression model, gives an indication of the "statistical significance" of the slope of the aging trend in the Y-axis. Data and regression trend lines were plotted utilizing an IBM-360/65 computer.

ORIGIN SYMBOL TABLE

<u>Origin</u>	<u>DOM</u>	<u>Wing</u>	<u>Symbol</u>
Motor 0012099	63166	2	0
Motor 0012199	63227	2	1
Motor STM-012	61221	1	S
Carton UP-7775	62075	1	U

TEST RESULTS

Regression analysis is the method of evaluation used in the analysis of the test results.

A. TENSILE:

Low rate (2.0 in/min) tensile testing data shows a statistically significant gradual decrease for strain at maximum stress and strain at rupture. Modulus shows a statistically significant gradual increase. Maximum stress and stress at rupture shows no significant change (Figures 1 thru 5).

The 20 in/min low rate tensile testing shows a statistically significant gradual decrease for strain at maximum stress and stress at rupture with the other regressions showing no significant change (Figures 6 thru 10).

The high rate strain parameters show a statistically significant gradual decrease (Figures 11 and 13). The stresses and modulus do not show a statistically significant change (Figures 12, 14 and 15).

High rate triaxial testing shows a statistically significant increase for strains and stresses (Figures 16 thru 19). The modulus shows a statistically significant decrease (Figure 20).

Case bond tensile shows a statistically significant decrease (Figure 21).

B. CREEP:

For both the 10 and 12 pound load no significant change is shown except for the 10 pound load at 20 sec which shows a statistically significant gradual decrease (Figures 22 thru 29).

C. STRESS RELAXATION:

Stress relaxation modulus for both 3 and 5% strain shows no significant change (Figures 30 thru 37).

D. CONSTANT STRAIN:

A statistically significant decrease is shown for constant strain (Figure 38).

E. SHORE HARDNESS:

The Shore A ten second hardness shows no significant change (Figure 39).

F. BURNING RATE:

A statistically significant decrease is shown for both the 500 and 1,000 psi initial testing (Figures 40 and 41).

G. HEAT OF EXPLOSION:

The heat of explosion does not show a significant change (Figure 42).

H. IGNITABILITY:

No significant change is seen in the data by the regression (Figure 43).

I. DIFFERENTIAL THERMAL ANALYSIS (DTA):

The endotherm and first exotherm do not show a significant change (Figures 43 and 45). The ignition temperature shows a statistically significant increase (Figure 46).

J. SOL GEL:

A statistically significant gradual decrease is shown for percent extractables, gel swell ratio, sol gel density and cross link density (Figures 47 thru 50).

K. FAILURE ENVELOPE:

Failure envelopes for STM-012 and 0012199 test data are shown in Figures 51 and 52 respectively.

CONCLUSIONS

The test results show that, under present storage conditions, some of the physical/mechanical and combustion properties of the propellant indicate statistically significant aging trends. On some regressions where a significant trend is indicated, the slope of the trend line is quite gradual and no operational problems are expected. On other regressions, i.e., triaxial tensile and burning rate, the slope of the trend line appears quite steep although, in reality, the percent change is minor as indicated by the formulas found at the top of each figure. The Y-axis range is automatically varied by the data spread to provide visibility between individual data means. As a result, the range values (on Y-axis) must be considered when visually analyzing regression slopes.

Although some aging trends have been observed, it does not appear that any significant degradation will occur in the propellant within the next two years.

RECOMMENDATIONS

It is recommended that continued testing be conducted on the three dissected motors and UP-7775 block propellant presently being tested and also on those motors selected for testing by Service Engineering. On those motors selected for future dissection, testing will include propellant, casebond and component materials.


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
54.0	26	159.0	24
73.0	24	160.0	5
75.0	2	166.0	5
82.0	5	167.0	5
87.0	5	168.0	16
94.0	16	175.0	8
97.0	7	190.0	3
104.0	5	191.0	5
106.0	5		
108.0	5		
116.0	5		
118.0	5		
123.0	4		
130.0	5		
133.0	15		
135.0	3		
140.0	5		
144.0	5		
145.0	3		
146.0	2		
149.0	3		
150.0	10		
152.0	3		
153.0	5		
157.0	3		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable for figures 1 thru 4.


$Y = ((+2.4539053E-01) + (-1.3523093E-04) * X_1$
 $F = +1.2625400E+01$ SIGNIFICANCE OF F = SIGNIFICANT $S_1 = +2.4699002E-02$
 $R = -2.2137482E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_2 = +3.8058658E-05$
 $t = +3.5532239E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_3 = +2.4125524E-02$
 $N = 247$ DEGREES OF FREEDOM = 245
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

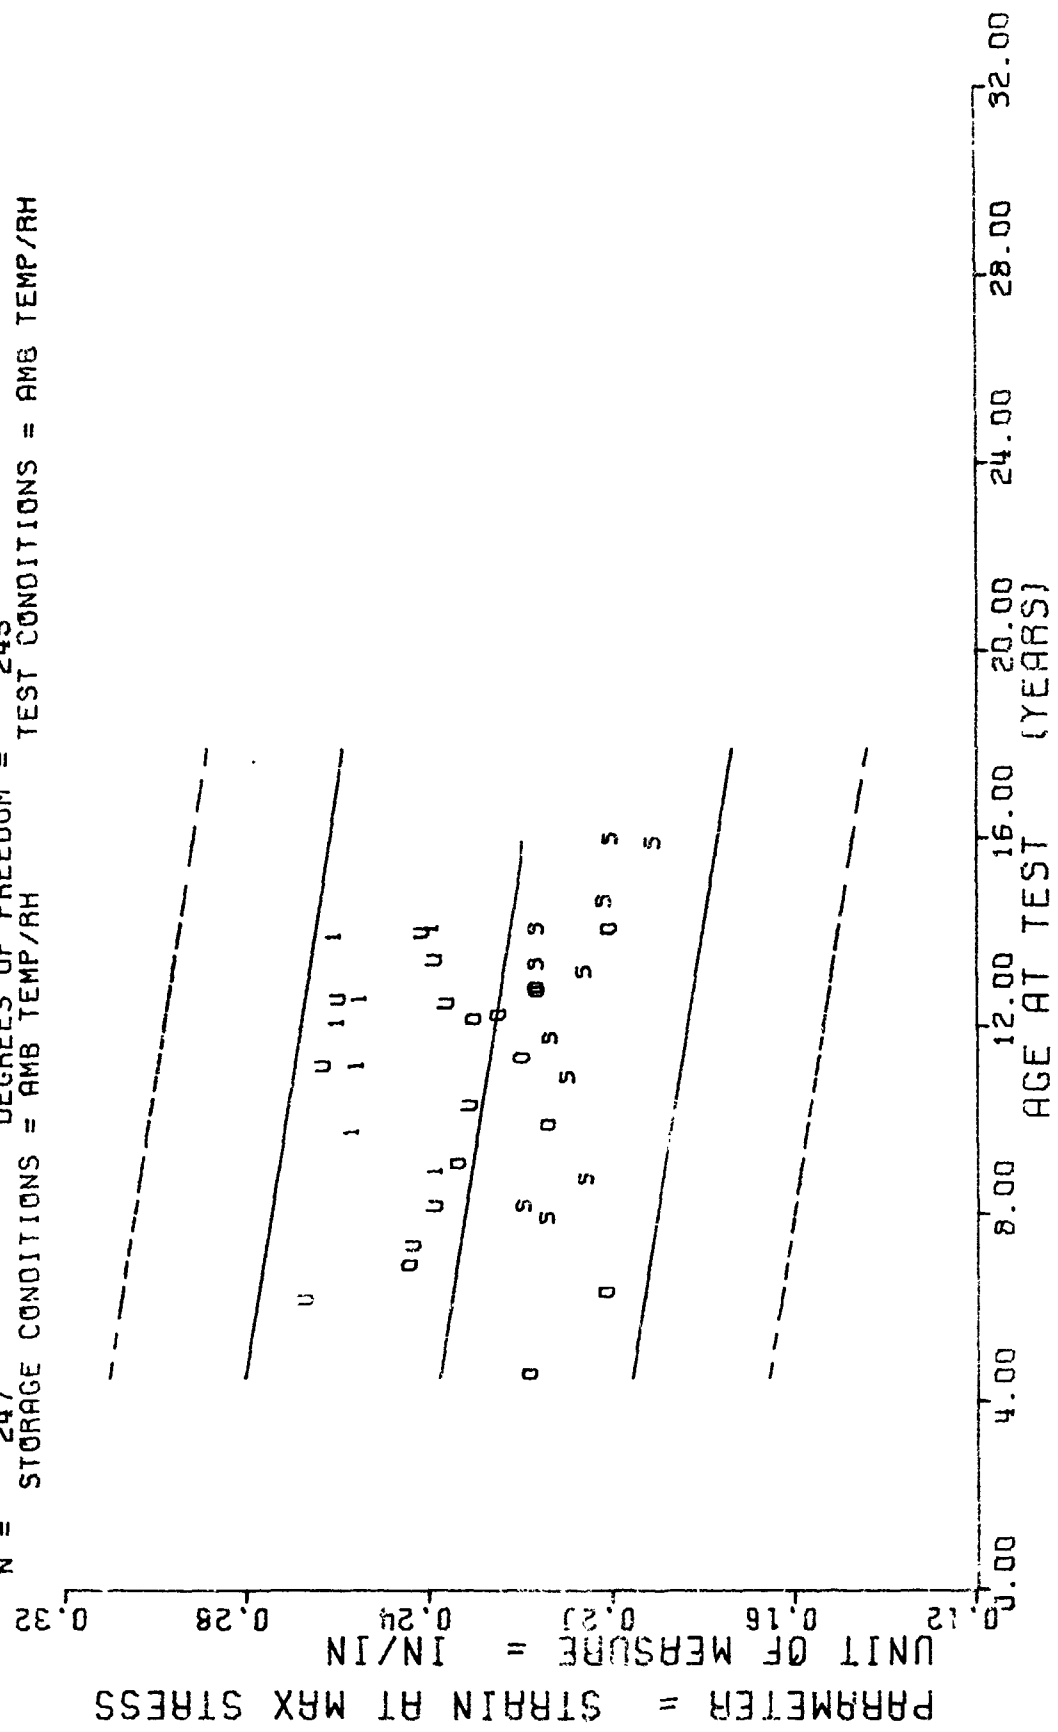

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN MAX STRESS

Figure 1


$Y = ((+1.1581648E+02) + (+1.0365111E-02) \times X)$
 F = +5.8814694E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT $G_1 = +8.5603296E+00$
 R = +4.8937211E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +1.3515467E-02$
 t = +7.6690738E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +8.5675045E+00$
 N = 247 DEGREES OF FREEDOM = 245
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

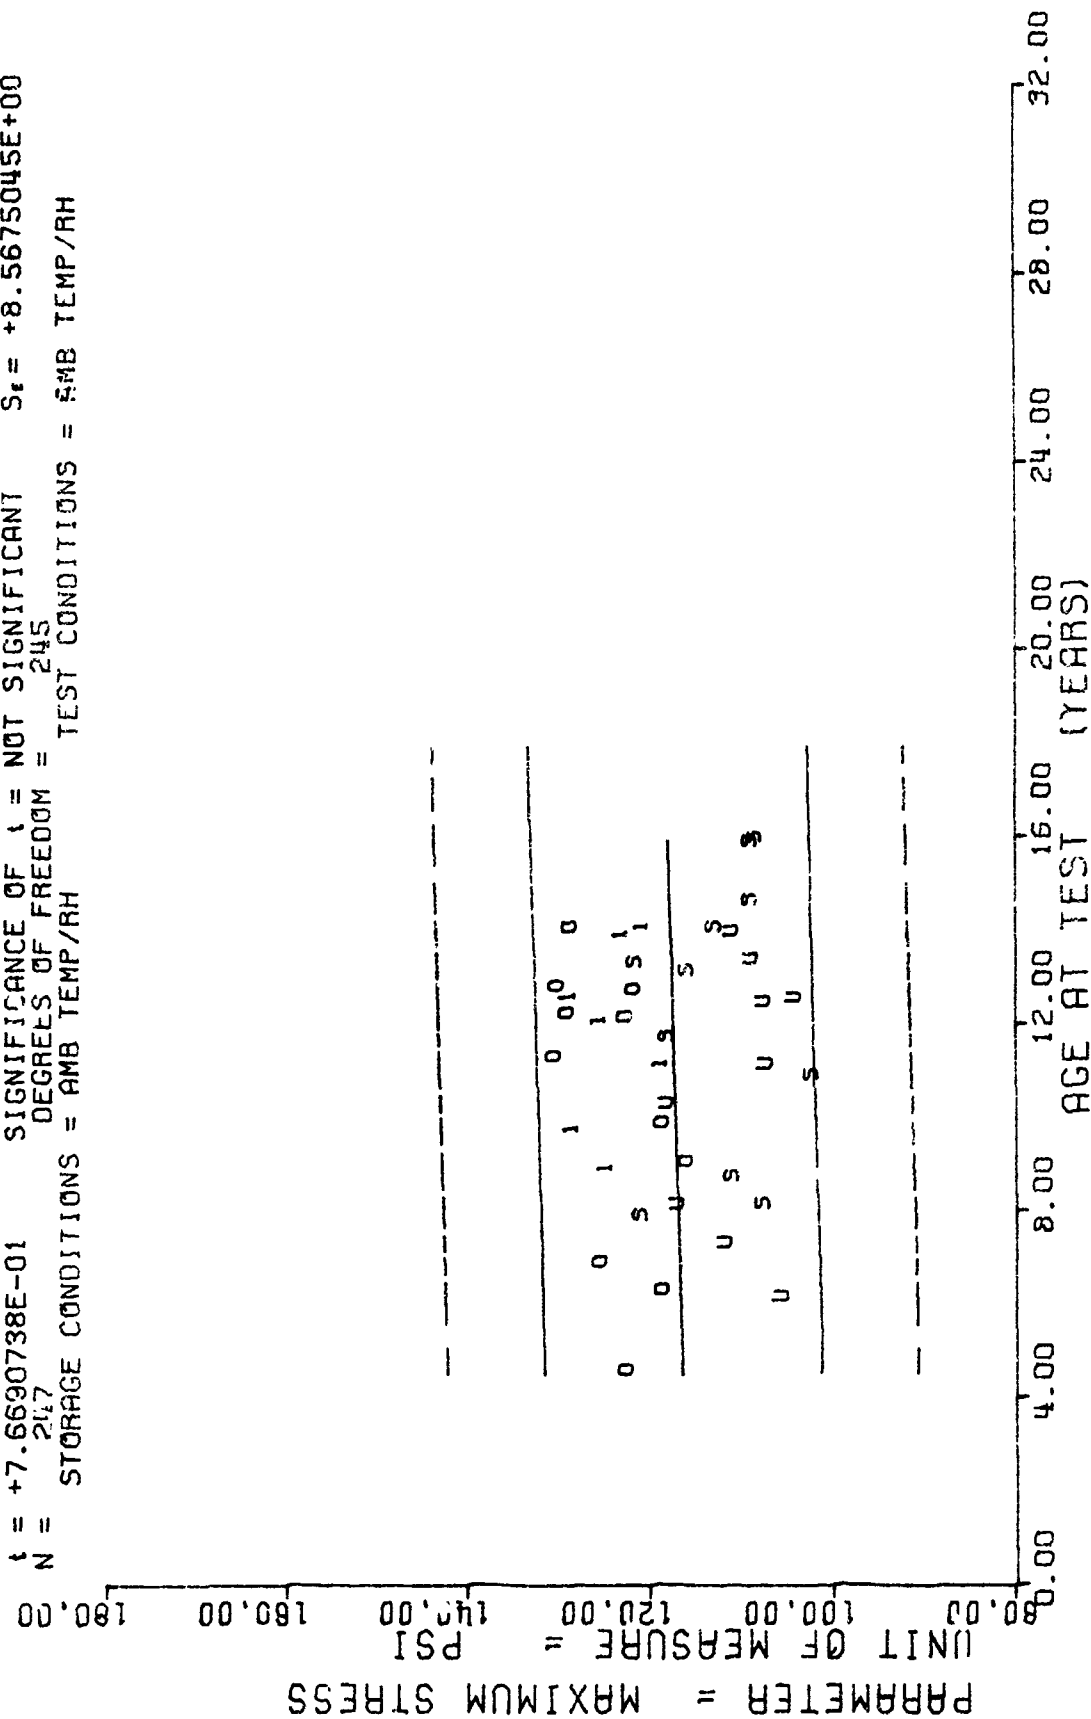

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MAXIMUM STRESS


Figure 2

$Y = ((+3.0619454E-01) + (-1.2476426E-04) * X)$
 $F = +7.2416470E+00$ SIGNIFICANCE OF F = SIGNIFICANT $\sigma_1 = +2.9760187E-02$
 $R = -1.6943779E-01$ SIGNIFICANCE OF R = SIGNIFICANT $\sigma_2 = +4.6363000E-05$
 $t = +2.6910308E+00$ SIGNIFICANCE OF t = SIGNIFICANT $\sigma_3 = +2.9389677E-02$
 $N = 247$ DEGREES OF FREEDOM = 245
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 77 DEG/F AMB-RH

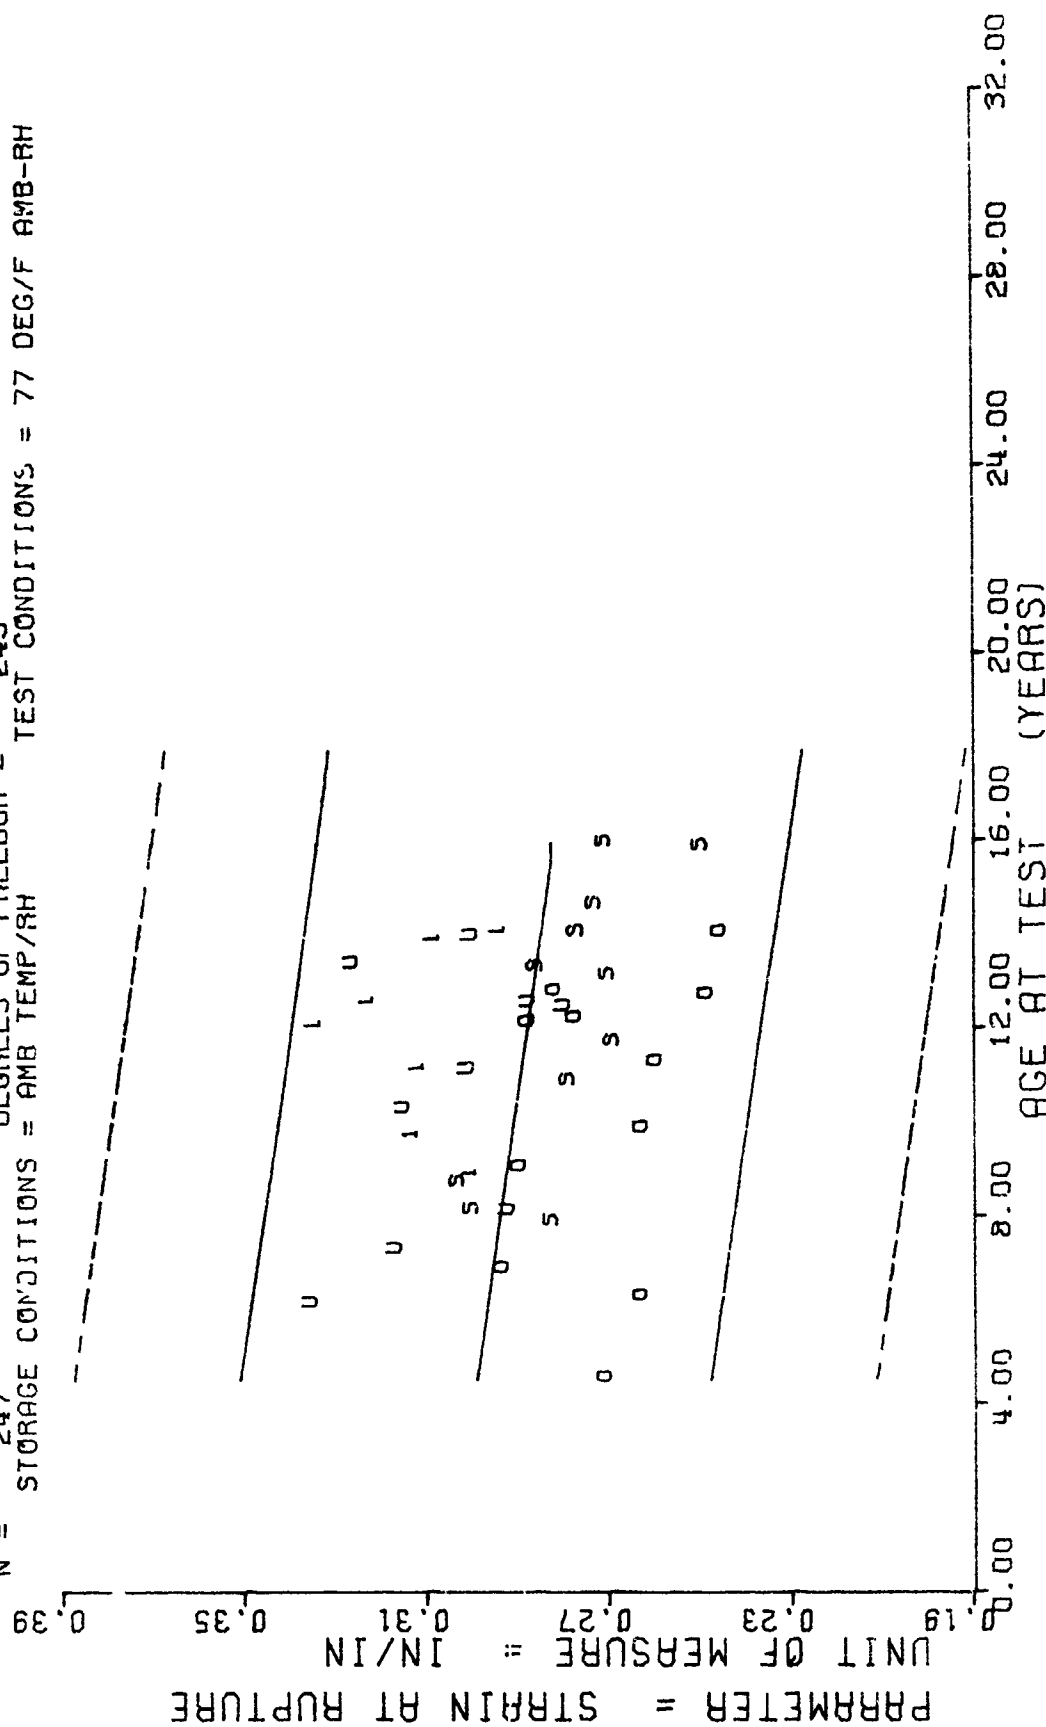

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN AT RUPTURE

F = +5.9501289E+00
 R = -1.5553912E-01
 I = +2.4392886E+00
 N = 242
 Y = ((+1.1168568E+02) + (-3.3215926E-02) * X)
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF I = SIGNIFICANT
 DEGREES OF FREEDOM = 240
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

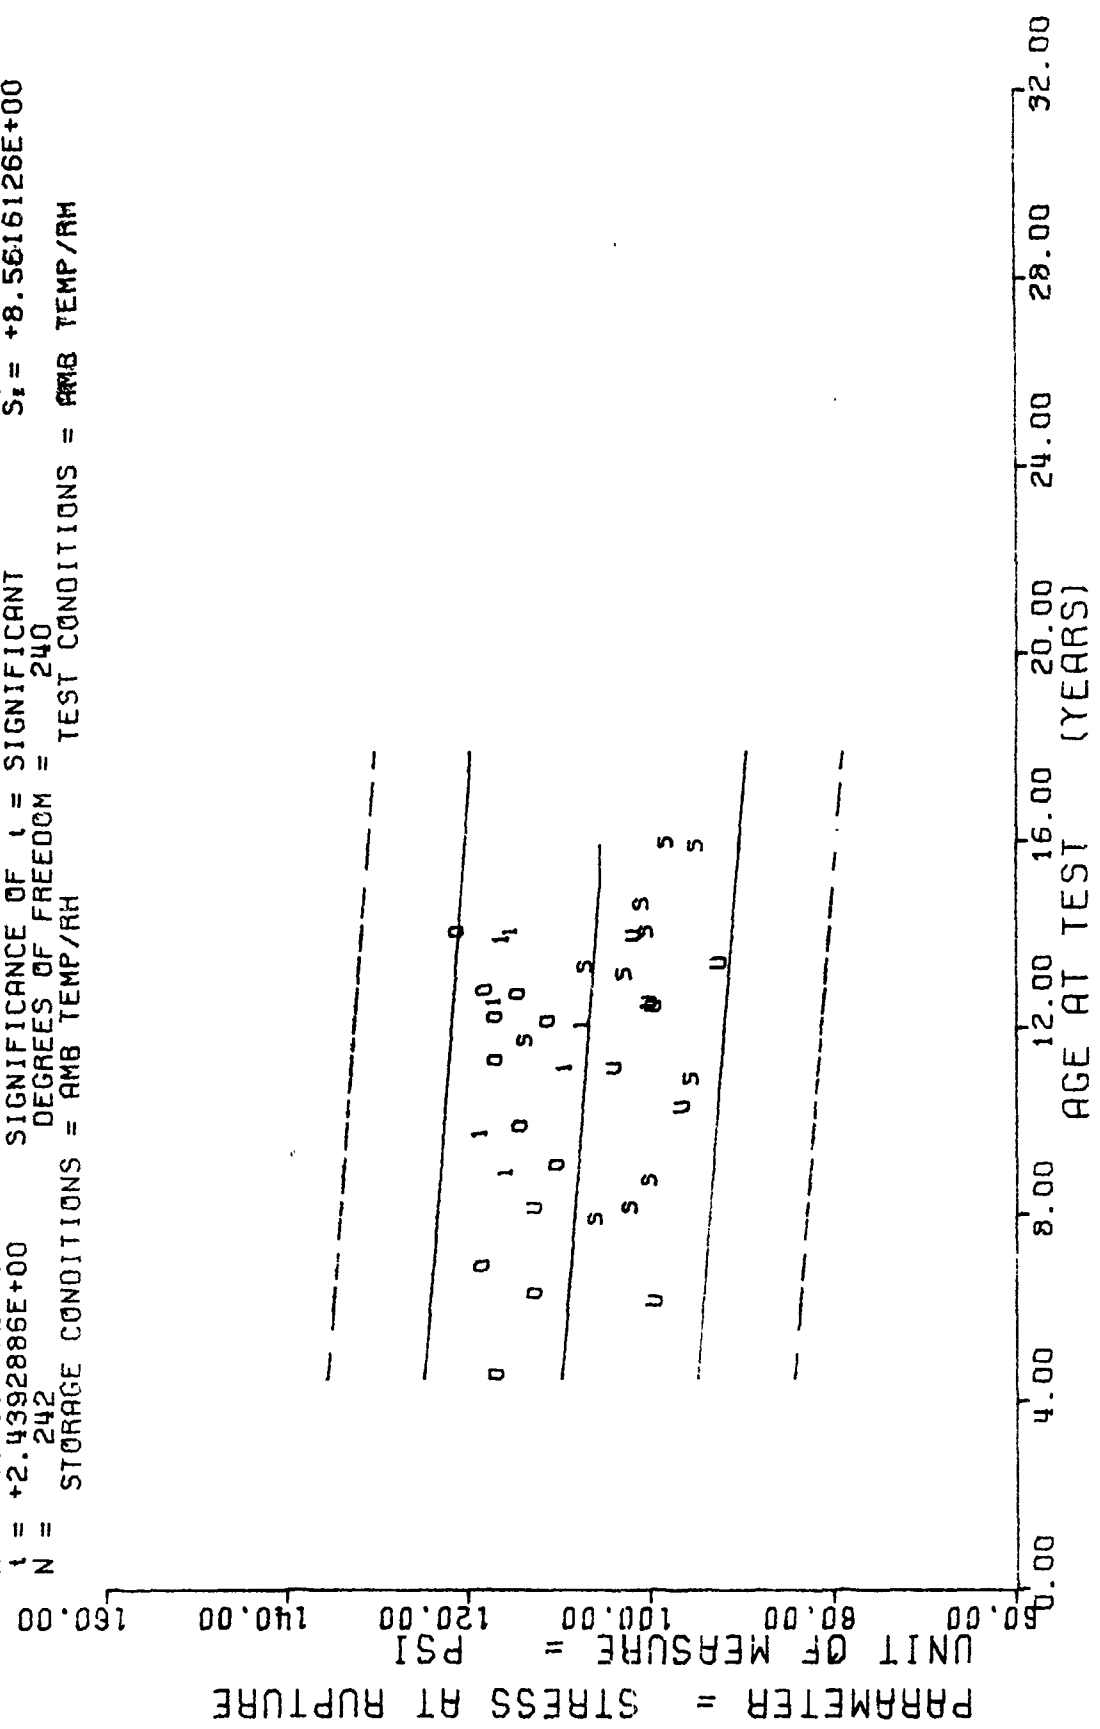

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRESS AT RUPTURE

Figure 4


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
54.0	26	168.0	16
73.0	24	175.0	8
82.0	5	190.0	3
87.0	5	191.0	5
94.0	16		
97.0	5		
104.0	5		
105.0	5		
108.0	5		
123.0	4		
130.0	5		
133.0	5		
135.0	3		
144.0	5		
145.0	3		
146.0	2		
149.0	3		
150.0	10		
152.0	3		
153.0	5		
157.0	3		
159.0	24		
160.0	5		
166.0	5		
167.0	5		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MODULUS

This sample size summary is applicable to figure 5

$Y = ((+9.6503183E+02) + (+1.1972605E+00) * X)$
 $F = +1.0767925E+01$ SIGNIFICANCE OF $F =$ SIGNIFICANT
 $R = +2.1790902E-01$ SIGNIFICANCE OF $R =$ SIGNIFICANT
 $t = +3.2814517E+00$ SIGNIFICANCE OF $t =$ SIGNIFICANT
 $N = 218$ DEGREES OF FREEDOM = 216
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

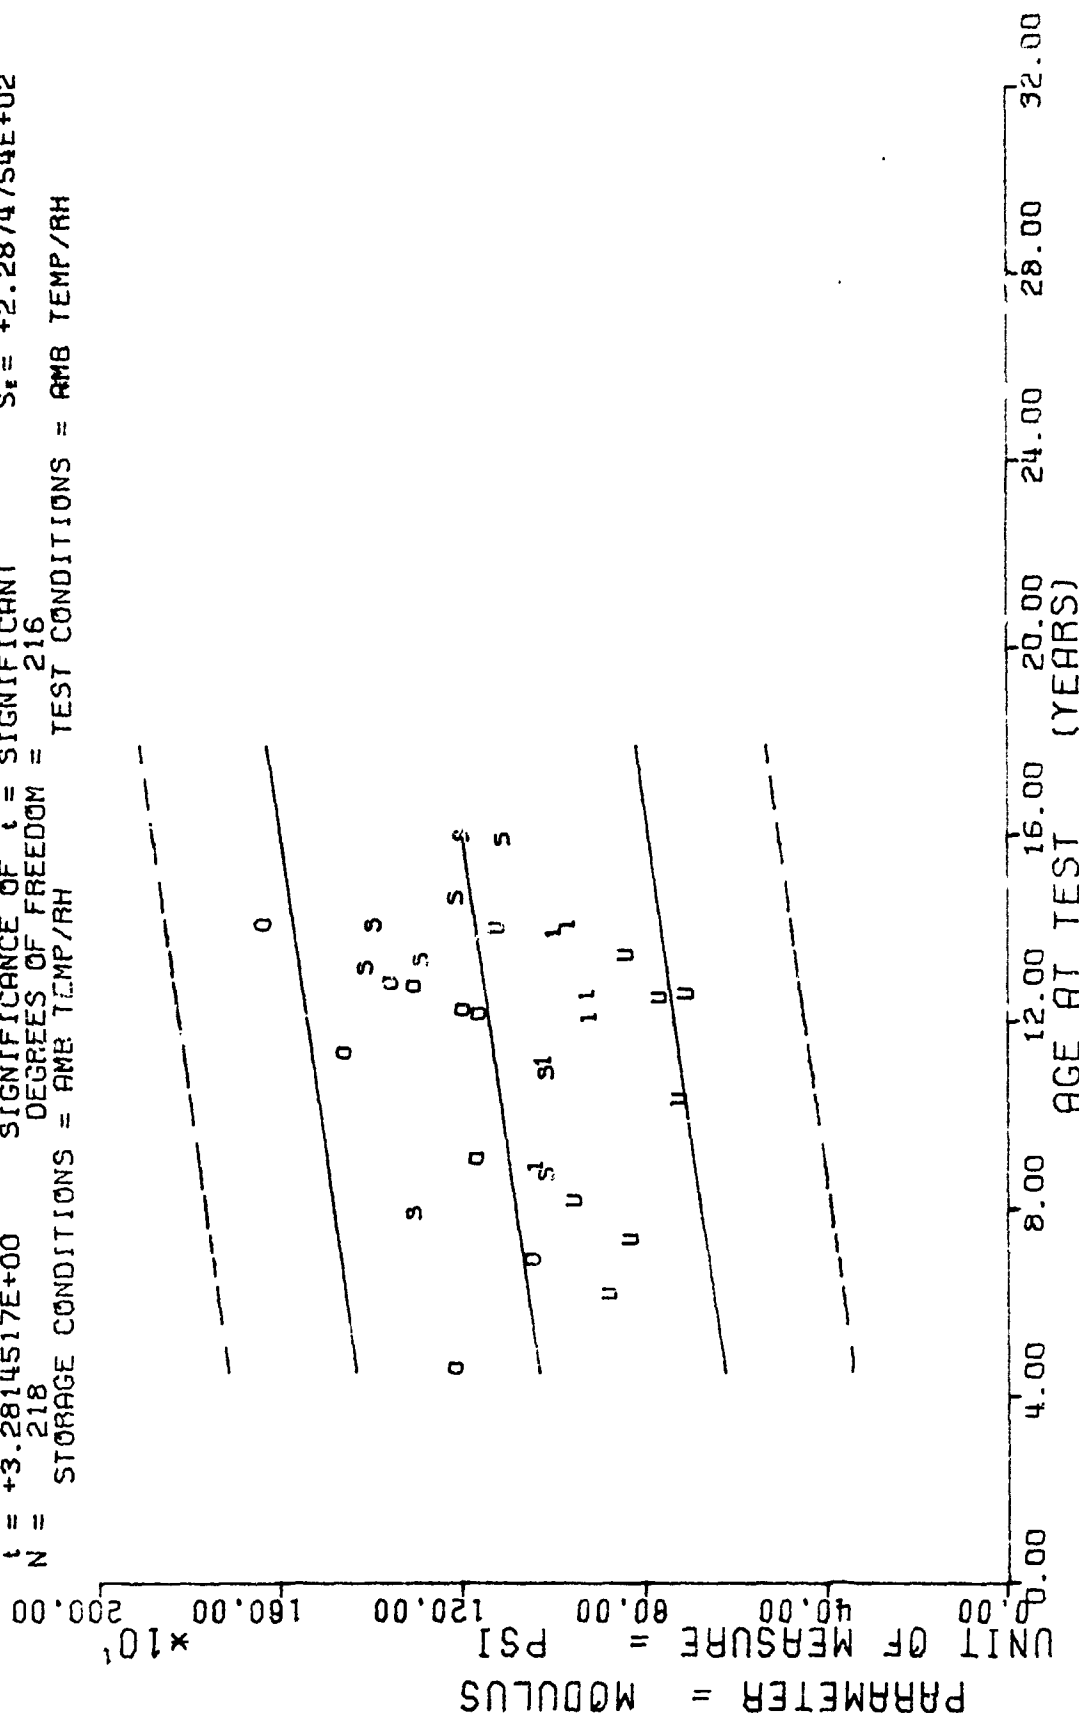

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MODULUS

Figure 5


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NP SAMPLES	AGE (MONTHS)	NP SAMPLES
82.0	2	191.0	5
97.0	5		
104.0	2		
106.0	5		
108.0	5		
116.0	5		
118.0	5		
123.0	5		
130.0	5		
133.0	14		
135.0	3		
140.0	5		
144.0	4		
145.0	3		
146.0	2		
150.0	9		
152.0	3		
153.0	5		
157.0	7		
160.0	5		
166.0	5		
167.0	7		
168.0	15		
175.0	8		
190.0	3		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable to figures 6 thru 9


$F = +2.1484889E+01$ SIGNIFICANCE OF $F = (-3.6255184E-04) * X)$
 $R = -3.6475446E-01$ SIGNIFICANCE OF $R =$
 $t = +4.6351795E+00$ SIGNIFICANCE OF $t =$
 $N = 142$ DEGREES OF FREEDOM = 140
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

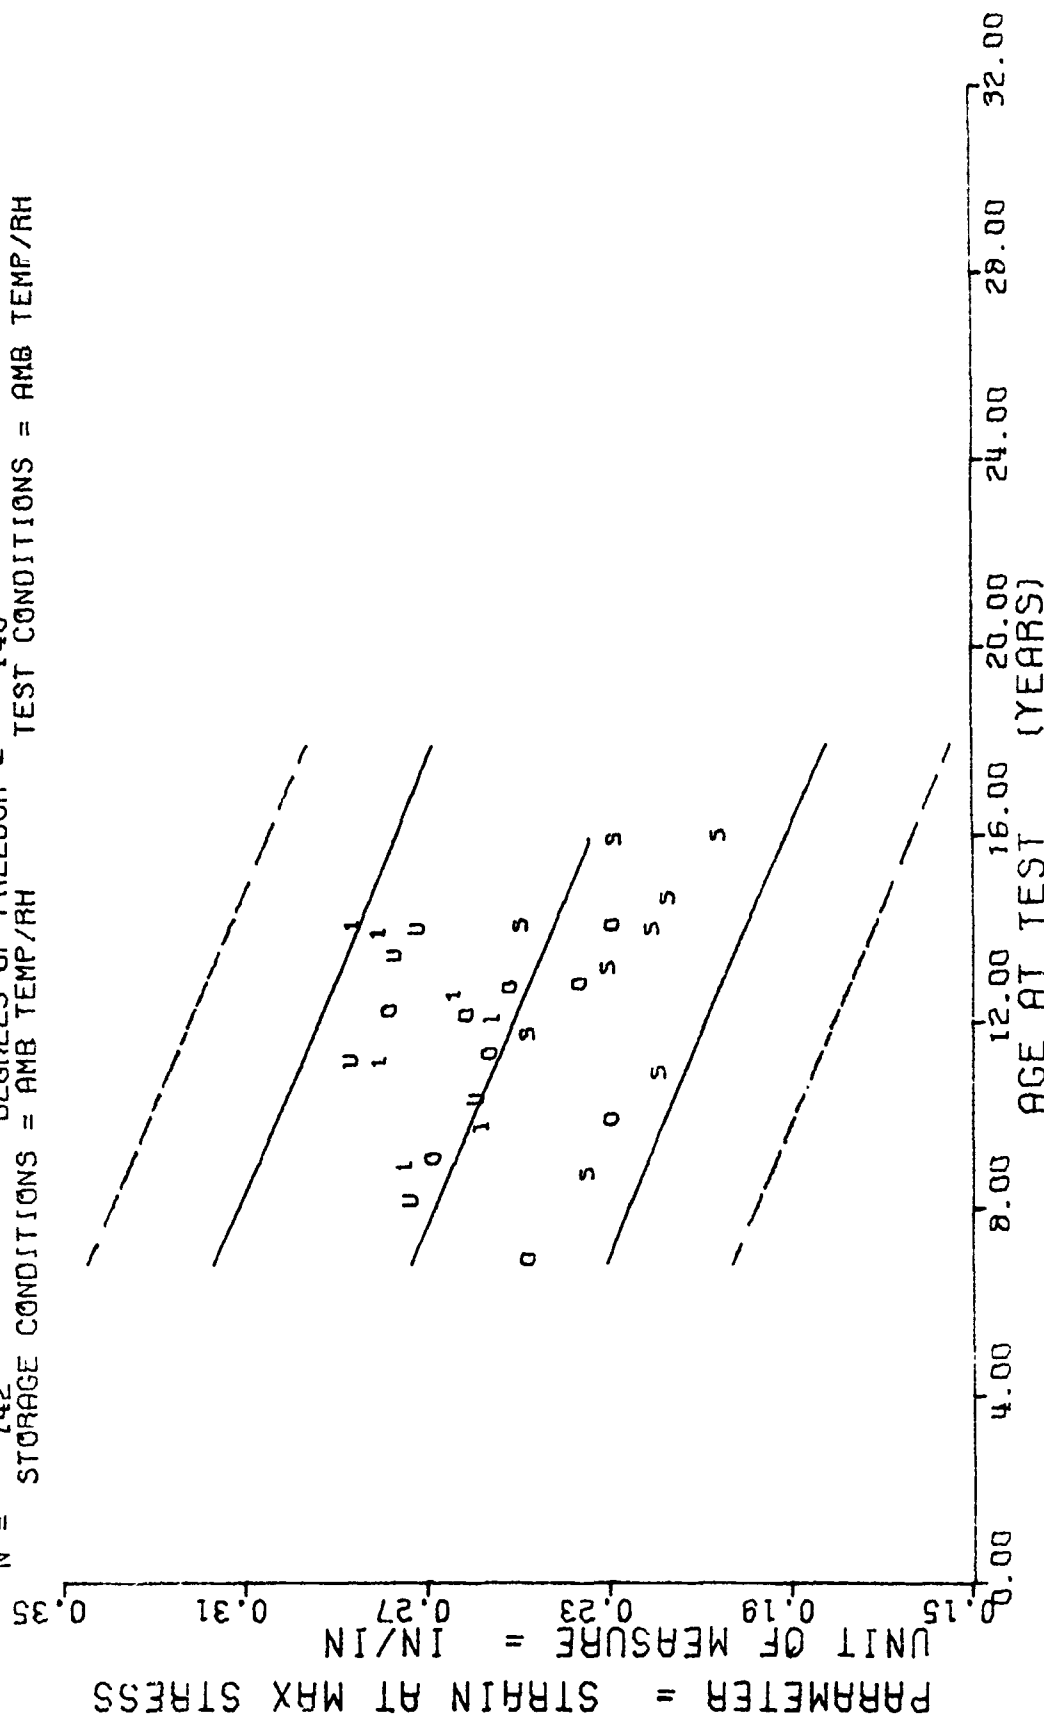

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN MAX STRESS

Figure 6


$F = +2.1811029E+00$
 $R = -1.2385602E-01$
 $t = +1.4768557E+00$
 $N = 142$
 $Y = ((+1.5364286E+02) + (-5.8101176E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $G = +1.1937372E+01$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +3.9341131E-02$
 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +1.1887687E+01$
 DEGREES OF FREEDOM = 140
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

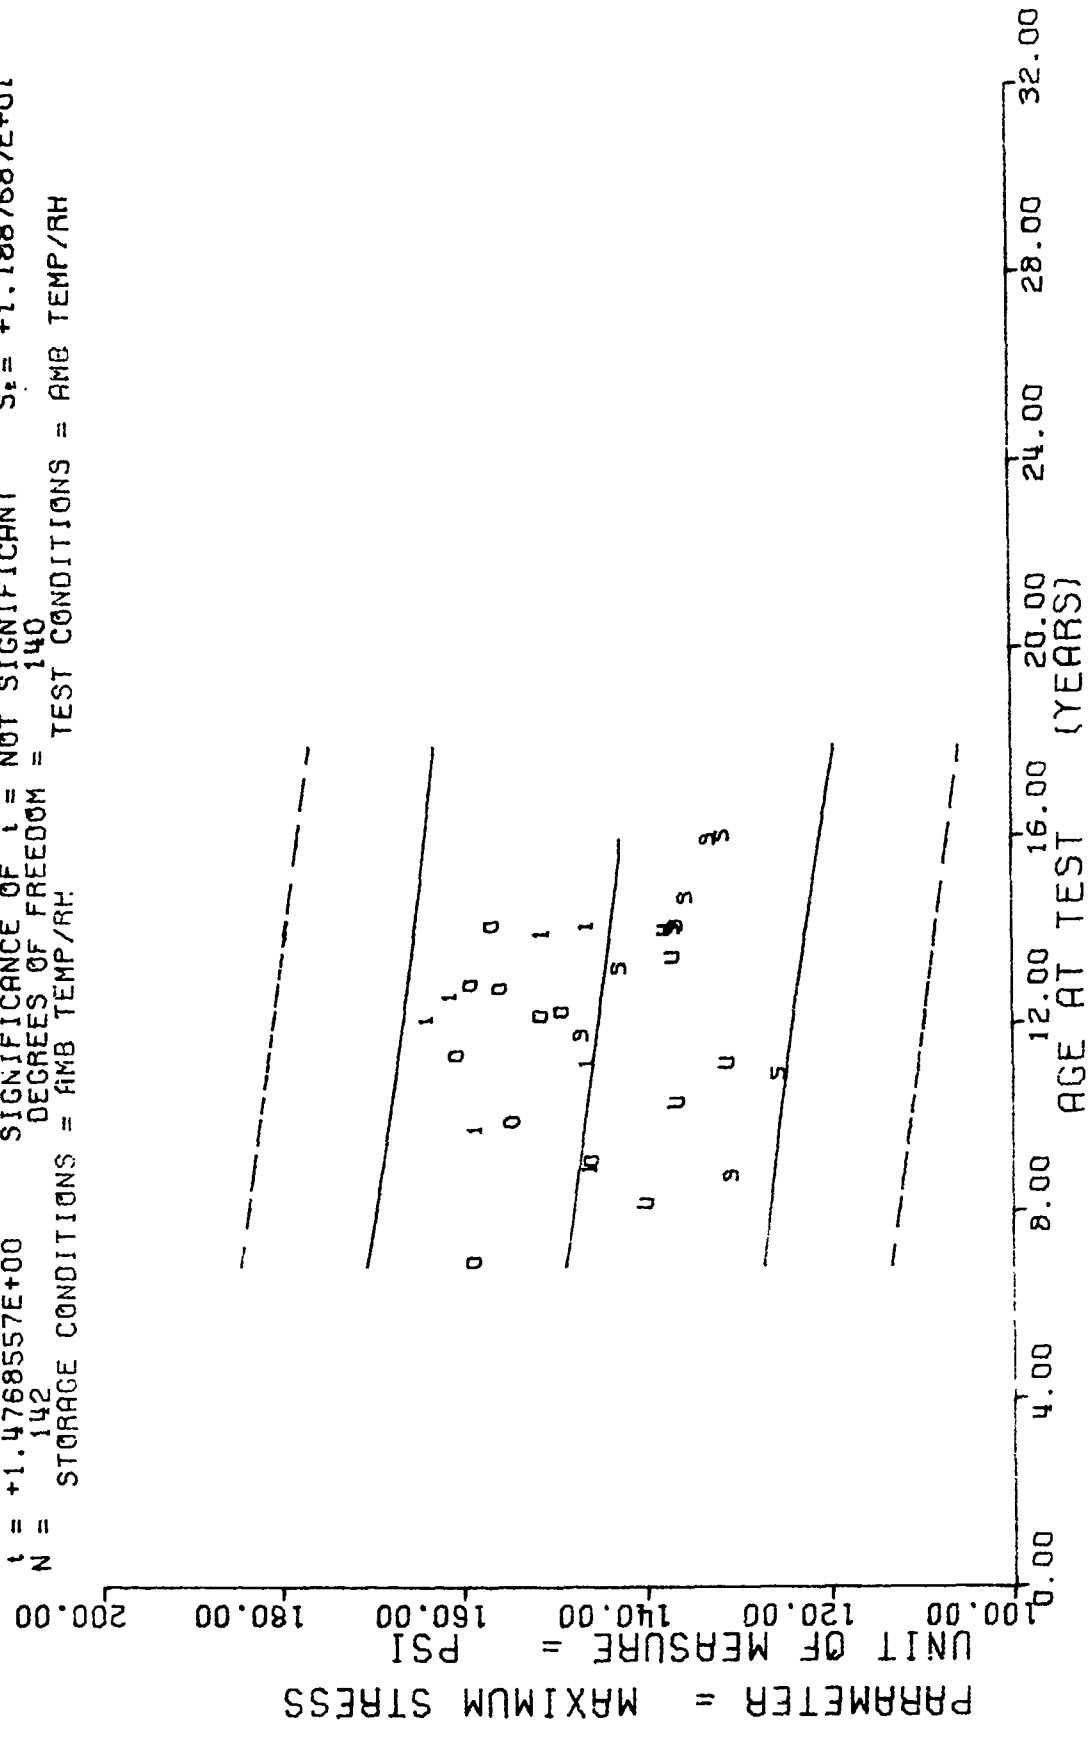

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MAXIMUM STRESS

Figure 7

$F = +3.6572193E+00$ SIGNIFICANCE OF $F =$ NOT SIGNIFICANT $G_1 = +2.7018881E-02$
 $R = -1.5955549E-01$ SIGNIFICANCE OF $R =$ NOT SIGNIFICANT $S_1 = +8.8585504E-05$
 $t = +1.9123857E+00$ SIGNIFICANCE OF $t =$ NOT SIGNIFICANT $S_2 = +2.6767831E-02$
 $N = 142$ DEGREES OF FREEDOM = 140
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

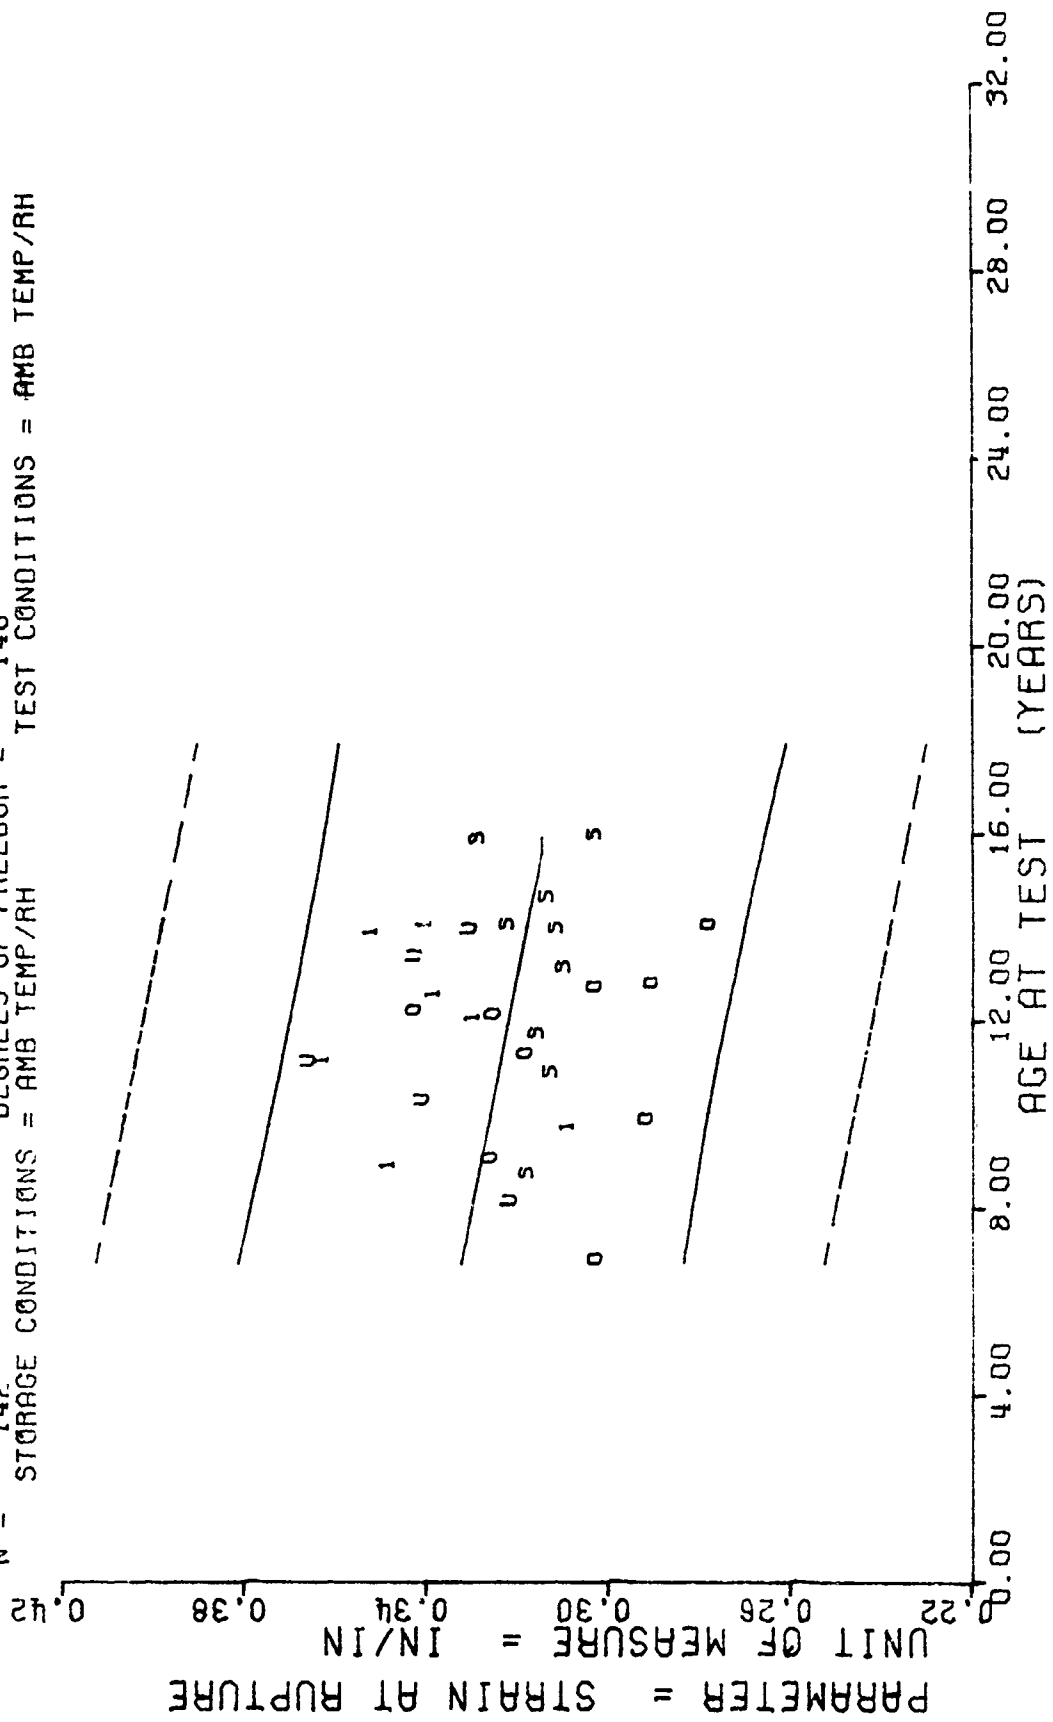


STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN AT RUPTURE

Figure 8

$F = +1.1004275E+01$
 $R = -2.6995172E-01$
 $t = +3.3172693E+00$
 $N = 142$

$Y = ((+1.5717854E+02) + (-1.3172797E-01) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 140

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

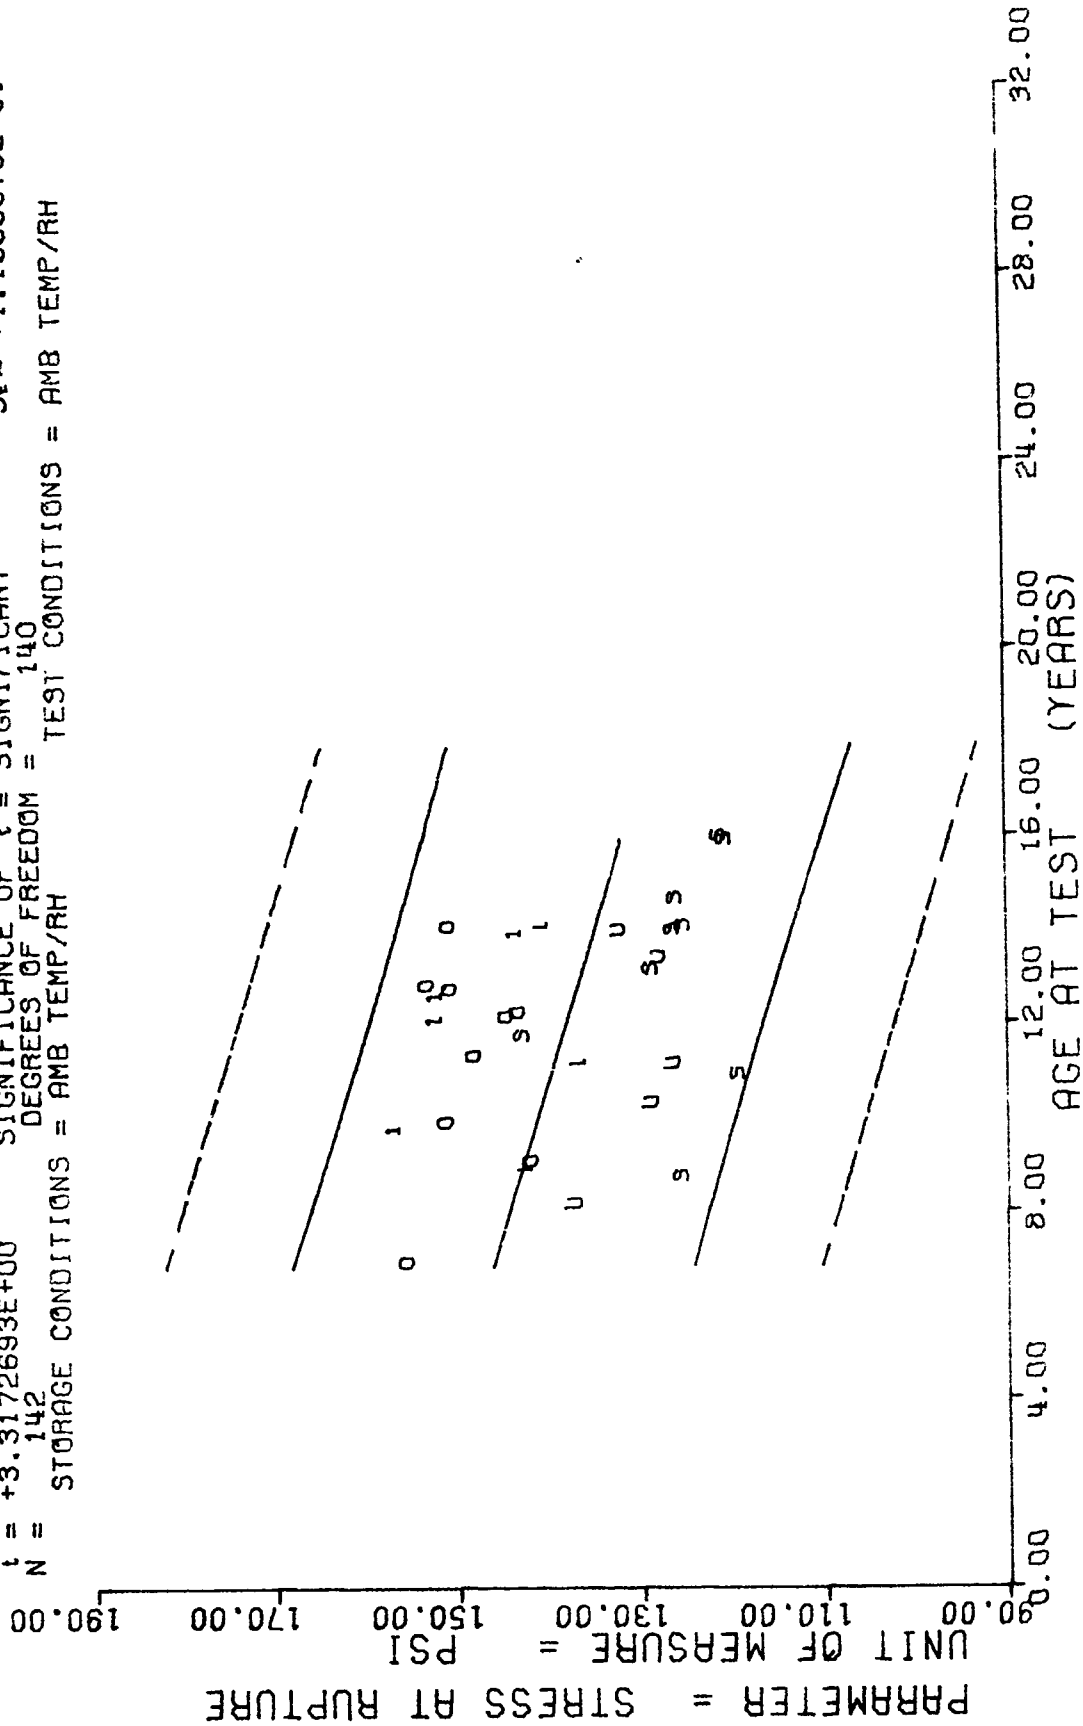

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRESS AT RUPTURE

Figure 9


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
92.0	2
97.0	5
104.0	2
123.0	5
133.0	4
135.0	3
144.0	4
145.0	3
146.0	2
150.0	9
152.0	3
153.0	5
157.0	7
160.0	5
166.0	5
167.0	7
168.0	15
175.0	8
190.0	3
191.0	5

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MODULUS

This sample size summary is applicable to figure 10

$Y = ((+1.7656764E+03) + (-3.5632900E-01) \times X)$
 $F = +3.7550096E-02$ SIGNIFICANCE OF $F =$ NOT SIGNIFICANT $G_y = +4.4631856E+02$
 $R = -1.9374210E-02$ SIGNIFICANCE OF $R =$ NOT SIGNIFICANT $S_1 = +1.8988472E+00$
 $t = +1.9377847E-01$ SIGNIFICANCE OF $t =$ NOT SIGNIFICANT $S_2 = +4.4846041E+02$
 $N = 102$ DEGREES OF FREEDOM = 100
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

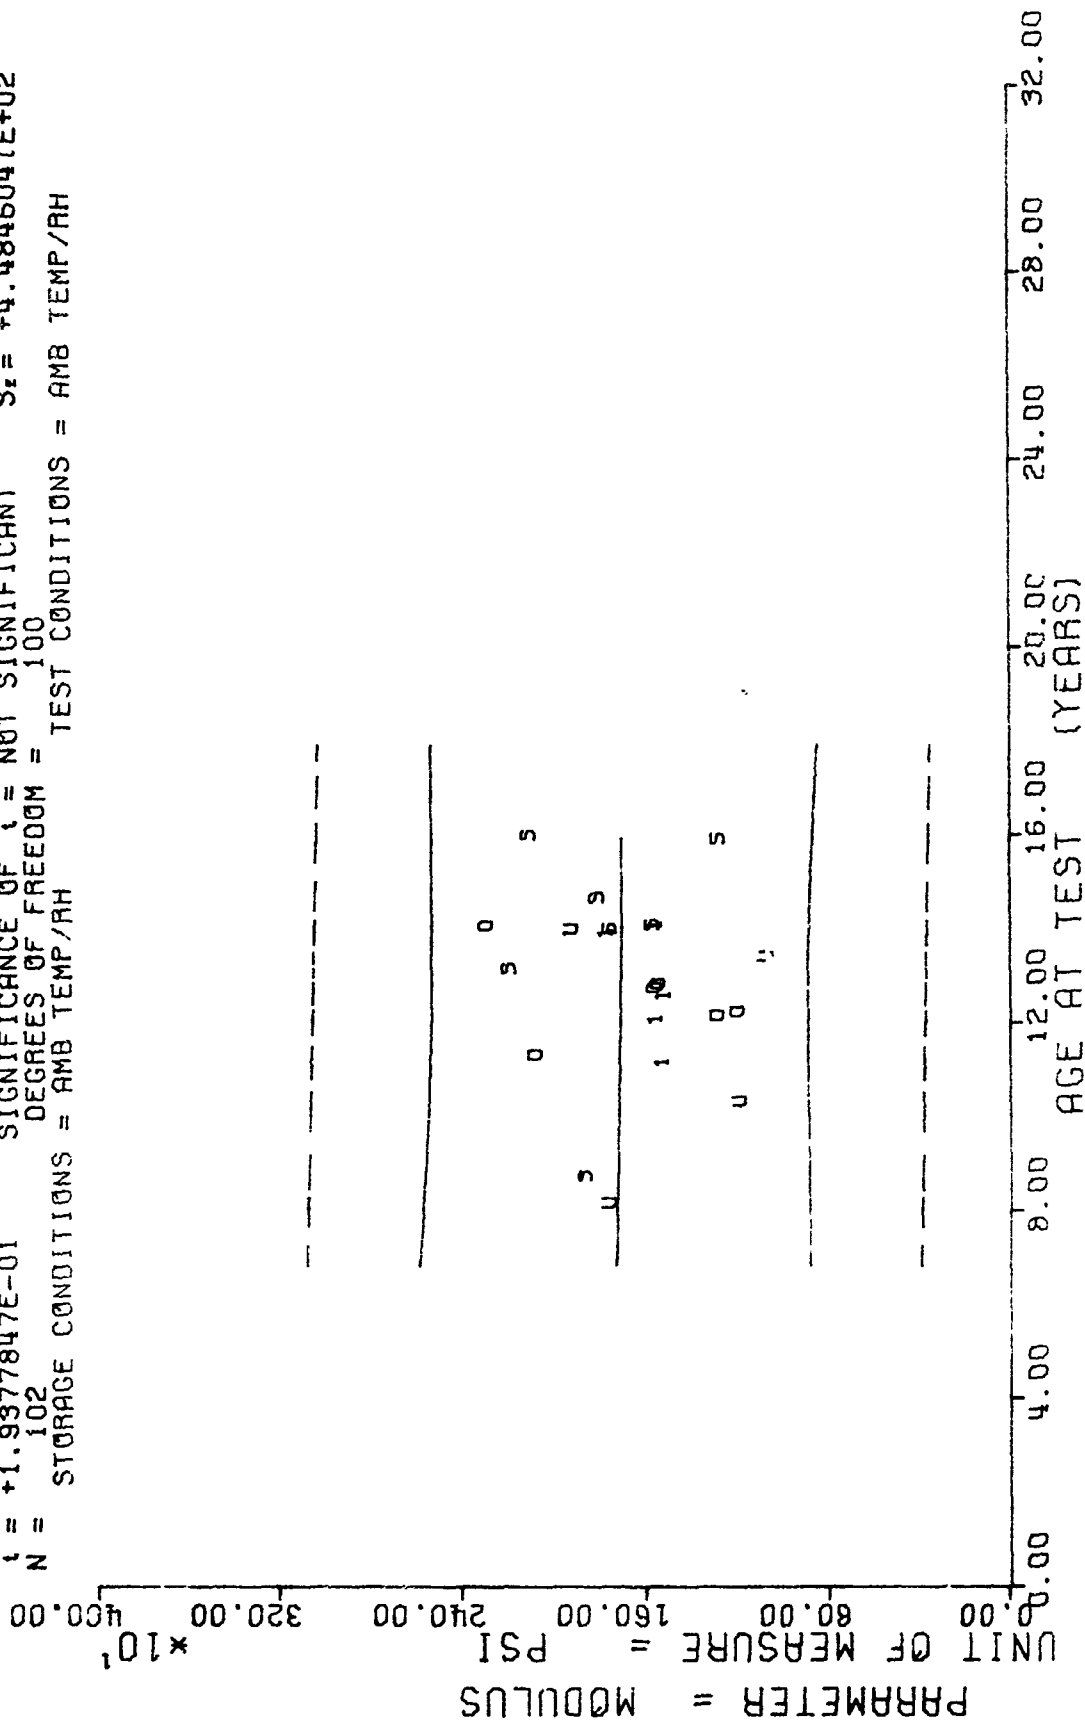

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MODULUS

Figure 10


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
60.0	6
71.0	4
80.0	16
83.0	5
93.0	6
105.0	6
107.0	5
109.0	5
116.0	6
118.0	6
131.0	5
134.0	5
136.0	4
141.0	6
144.0	5
146.0	5
151.0	5
154.0	5
158.0	5
168.0	5
176.0	5

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable to figures 11 thru 15


F = +7.8894404E+00
 R = -2.5033896E-01
 t = +2.8088147E+00
 N = 120
 STORAGE CONDITIONS = AMB TEMP/RH
 Y = ((+2.3415426E-01) + (-4.1258261E-04) * X)
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 118
 TEST CONDITIONS = AMB TEMP/RH
 G = +5.3875752E-02
 S_p = +1.4688850E-04
 S_e = +5.2380806E-02

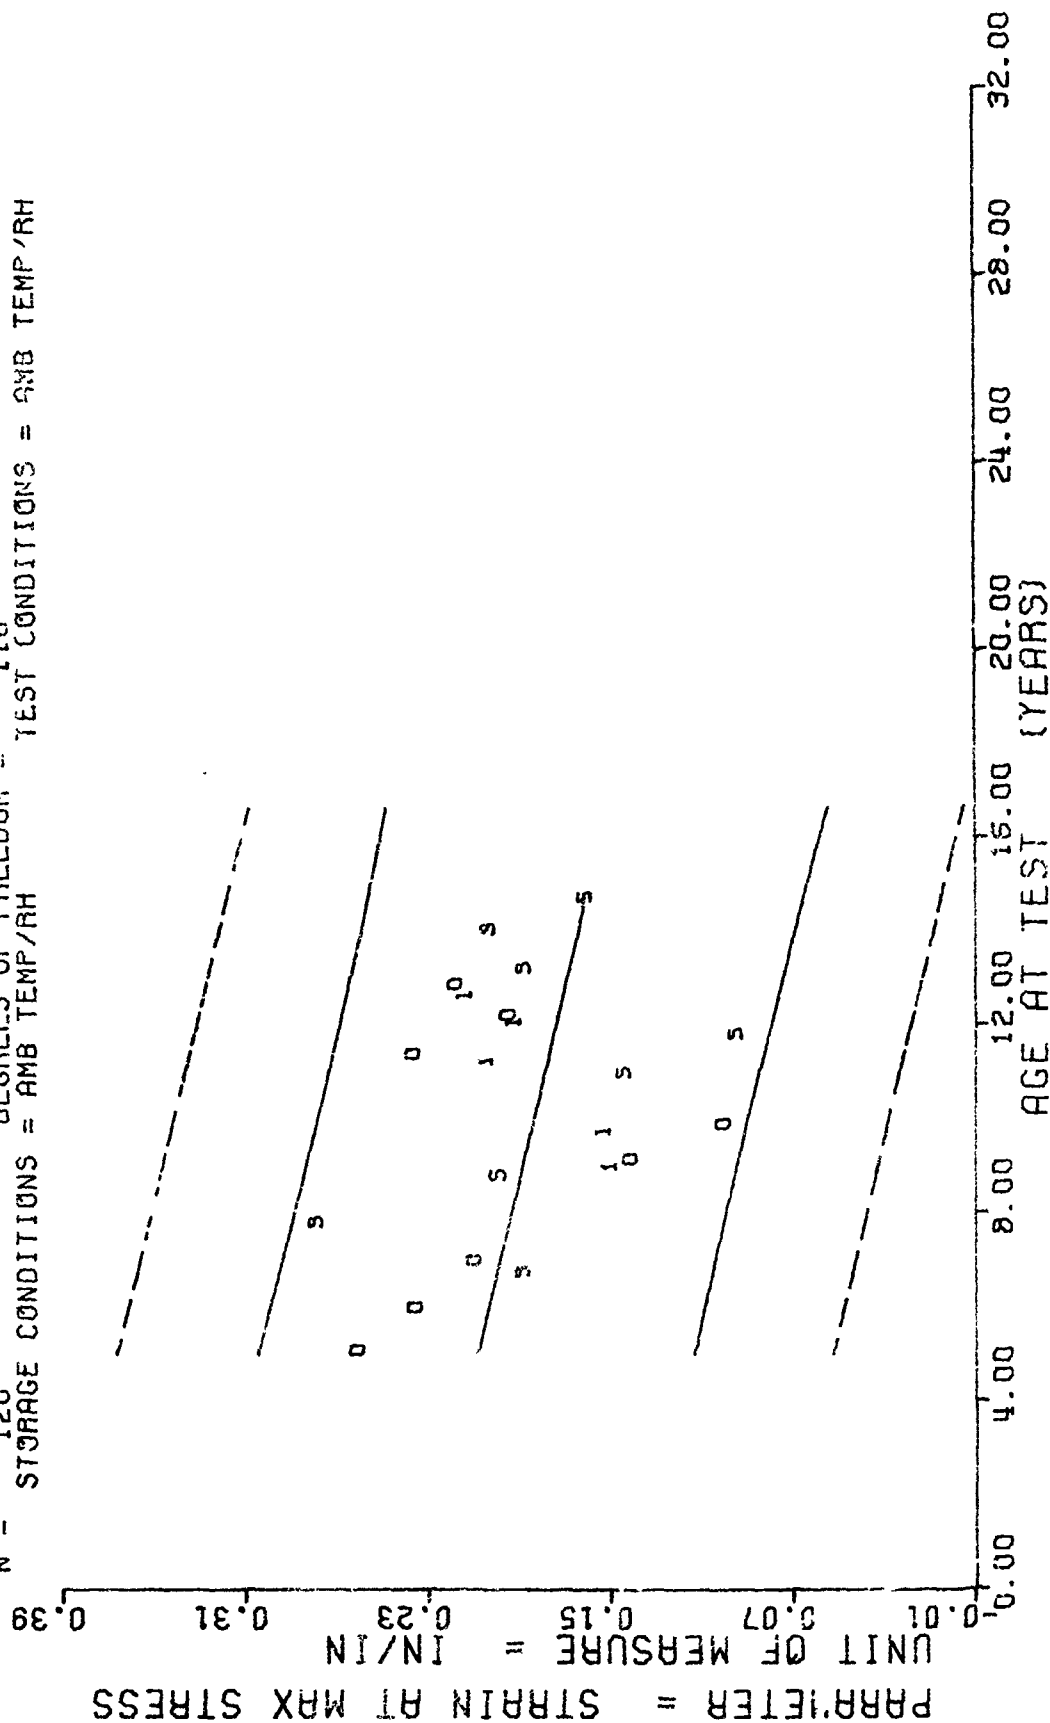

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRAIN MAX STRESS

Figure 11

F = +9.2661460E-02
 R = +2.8011612E-02
 t = +3.0440345E-01
 N = 120
 STORAGE CONDITIONS = AMB TEMP/RH
 Y = ((+3.2990084E+02) + (+3.4467603E-02) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 118
 TEST CONDITIONS = AMB TEMP/RH
 S₀ = +4.0223869E+01
 S₁ = +1.1323000E-01
 S₂ = +4.0378099E+01

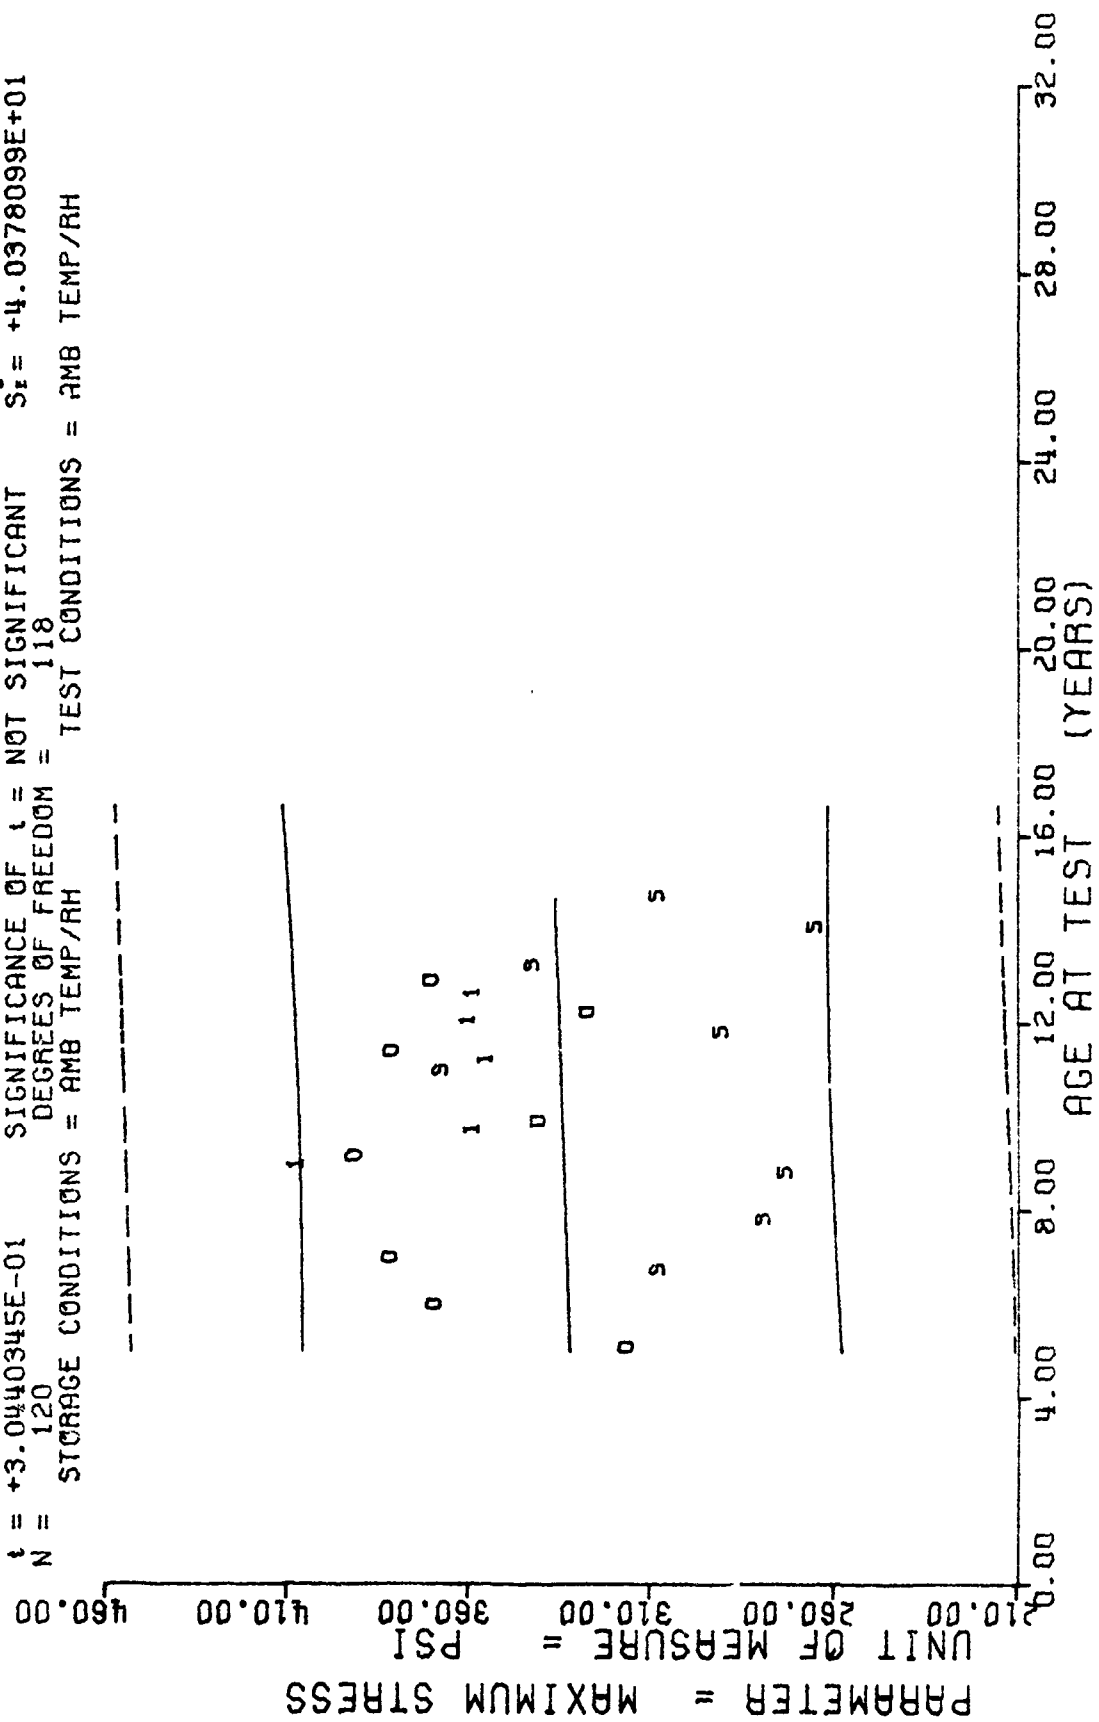

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, MAXIMUM STRESS

F	=	+4.8571021E+00	Y	=	{ (+3.5847478E-01) + (-1.8334907E-04) * X1		+3.0144016E-02
A	=	-1.9883300E-01			SIGNIFICANCE OF F	=	SIGNIFICANT
R	=	+2.2038834E+00			SIGNIFICANCE OF A	=	SIGNIFICANT
t	=				SIGNIFICANCE OF t	=	SIGNIFICANT
N	=	120			DEGREES OF FREEDOM	=	118
					STORAGE CONDITIONS = AMB TEMP/RH		TEST CONDITIONS = AMB TEMP/RH


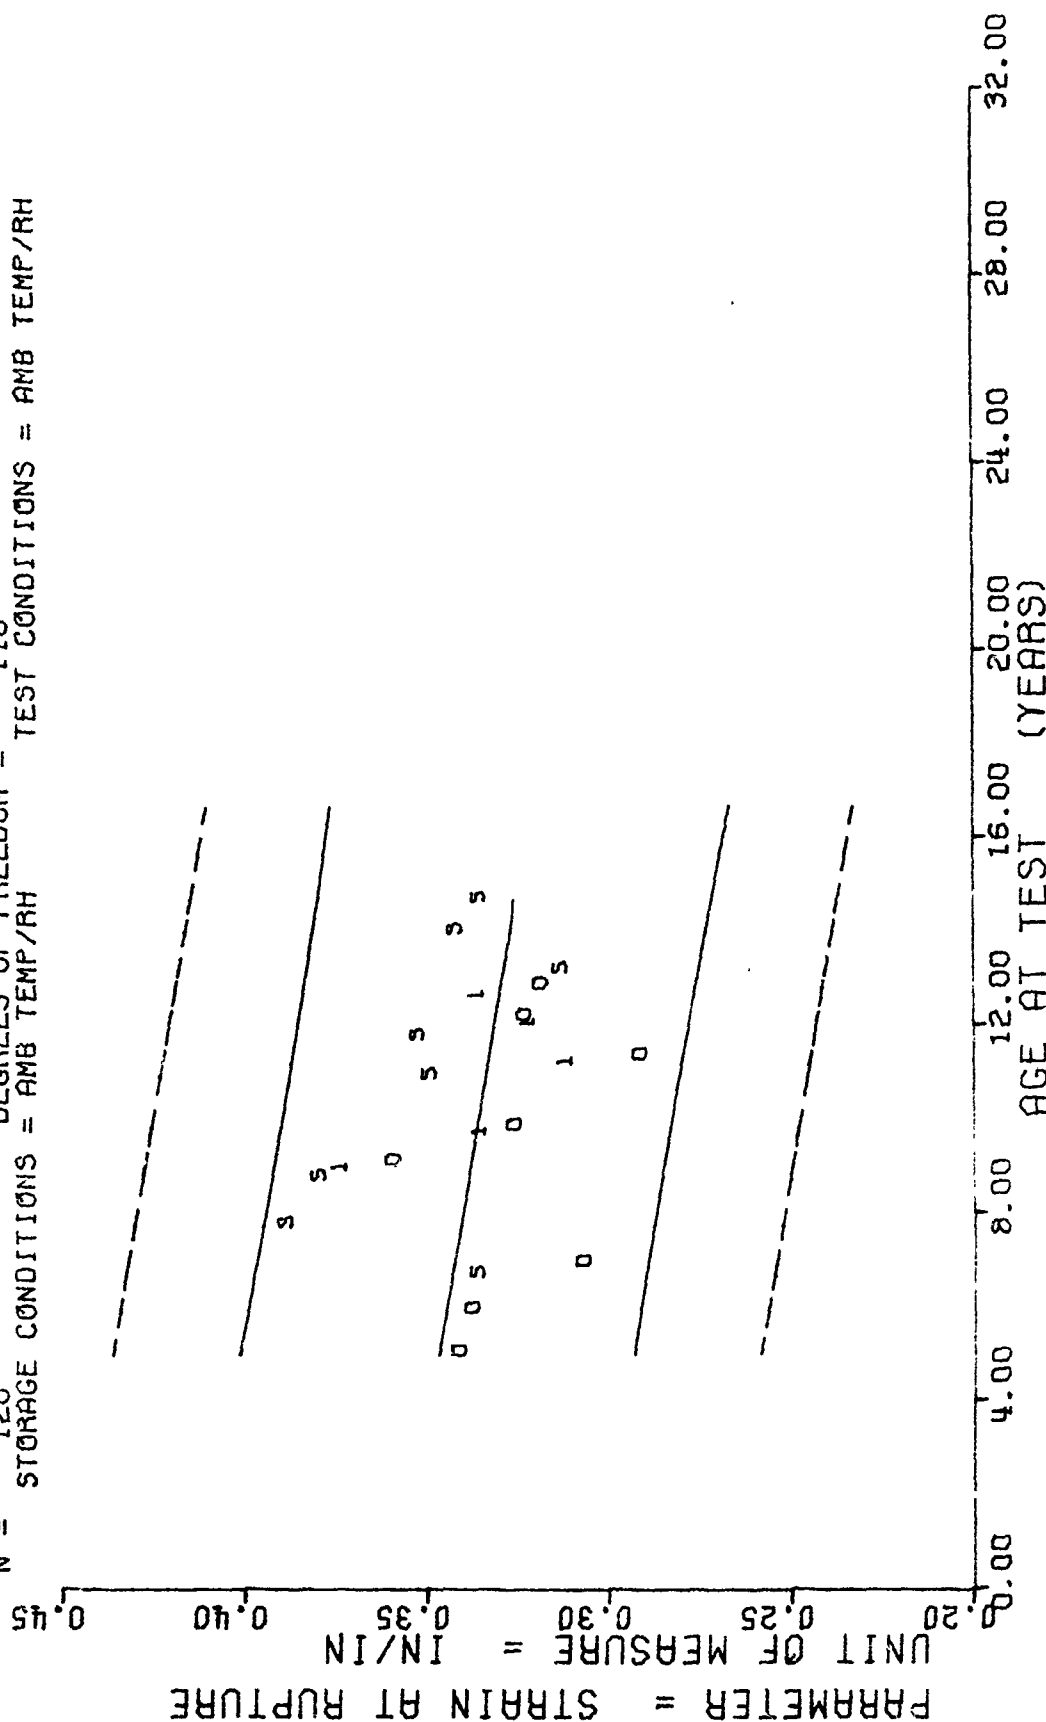


Figure 13

$Y = ((+2.9348870E+02) + (-3.3866325E-02) \times X)$
 $F = +8.4602215E-02$ SIGNIFICANCE OF F = NOT SIGNIFICANT $G_1 = +4.1360398E+01$
 $R = -2.6766663E-02$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +1.1643330E-01$
 $t = +2.9086459E-01$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +4.1520402E+01$
 $N = 120$ DEGREES OF FREEDOM = 118
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

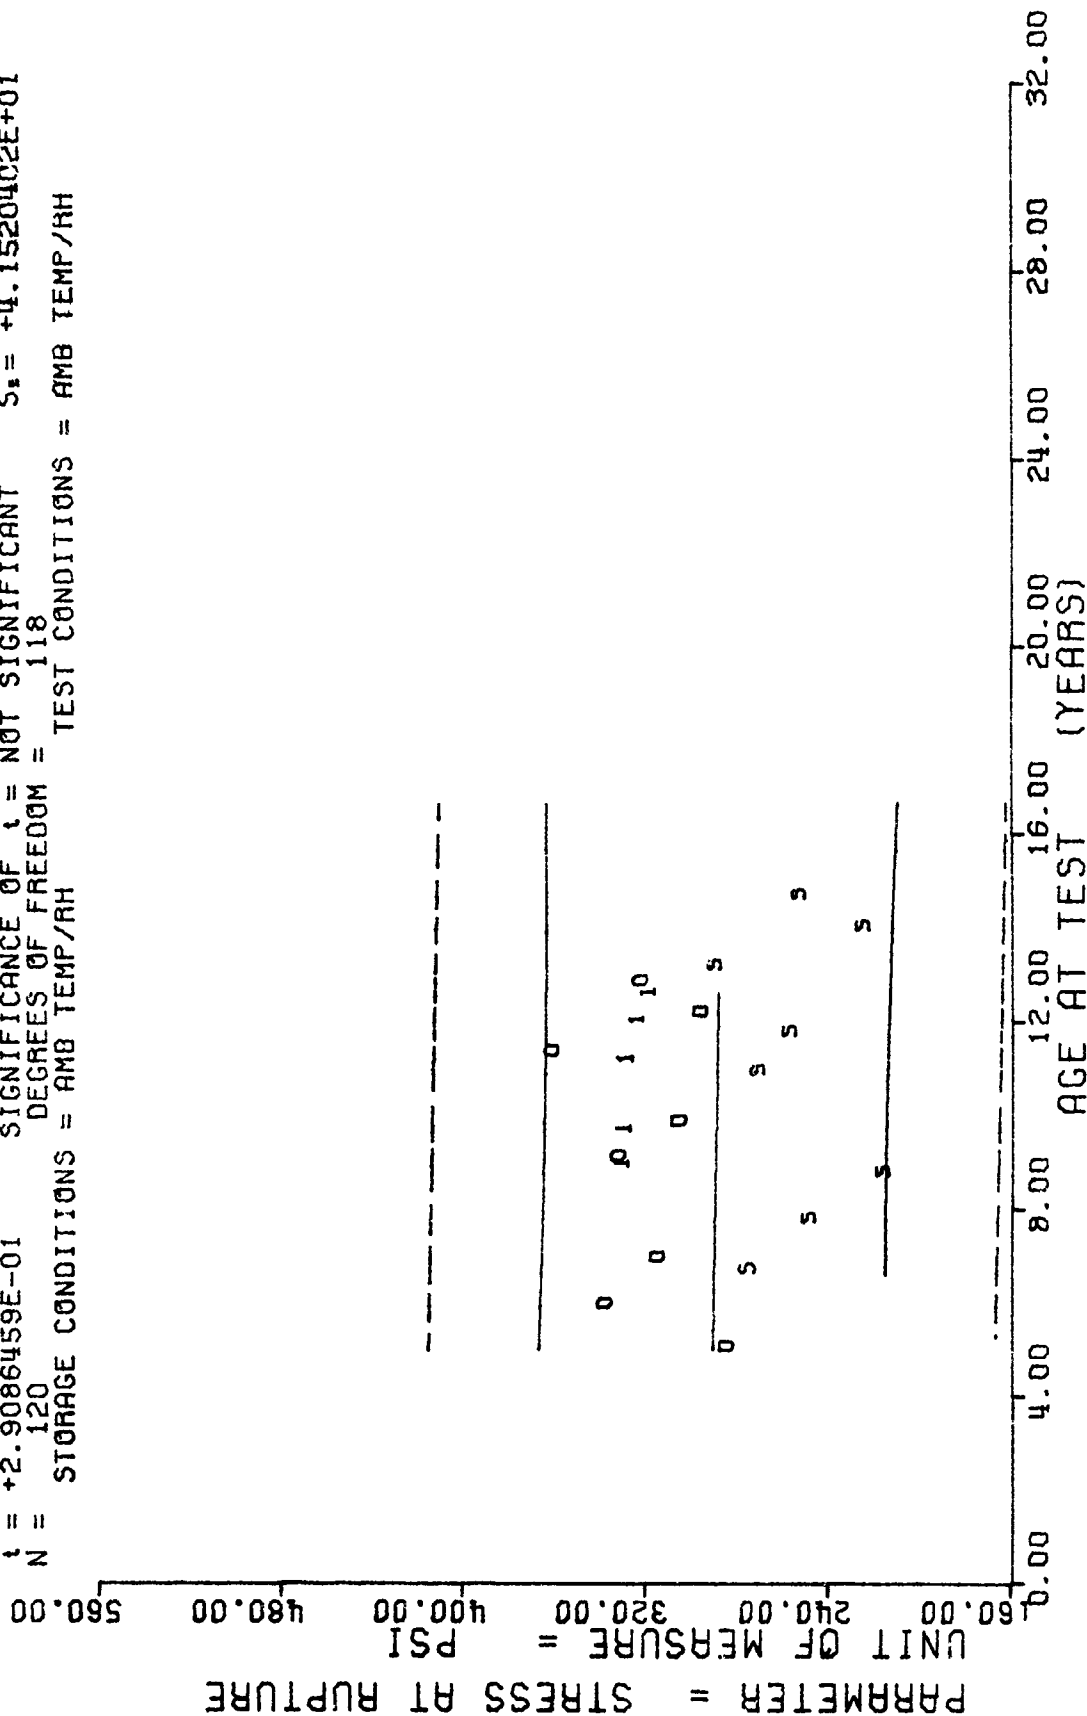

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRESS AT RUPTURE

Figure 14

	(+6.7608705E+03)	(8.2608309E-01)	(X)
F = +2.3205939E-02	SIGNIFICANCE OF F =	NOT SIGNIFICANT	W = +1.9258334E+03
R = -1.4022190E-02	SIGNIFICANCE OF R =	NOT SIGNIFICANT	S = +5.4228070E+00
N = +1.5233495E-01	SIGNIFICANCE OF t =	NOT SIGNIFICANT	S = +1.9337864E+03
	DEGREES OF FREEDOM =	118	
	STORAGE CONDITIONS =	AMB TEMP/°RH	
		TEST CONDITIONS =	AMB TEMP/°RH


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
71.0	2
72.0	8
83.0	2
93.0	2
105.0	2
108.0	2
110.0	2
132.0	2
134.0	4
136.0	2
144.0	2
146.0	2
151.0	3
153.0	3
158.0	2
168.0	2
175.0	3

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, STRAIN MAX STRESS

This sample size summary is applicable to figures 16 thru 20

$Y = ((+8.6675837E-02) + (+1.0457370E-03) * X)$
 $F = +8.3577218E+01$ SIGNIFICANCE OF F = SIGNIFICANT
 $R = +8.1258010E-01$ SIGNIFICANCE OF R = SIGNIFICANT
 $t = +9.1420576E+00$ SIGNIFICANCE OF t = SIGNIFICANT
 $N = 45$ DEGREES OF FREEDOM = 43
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

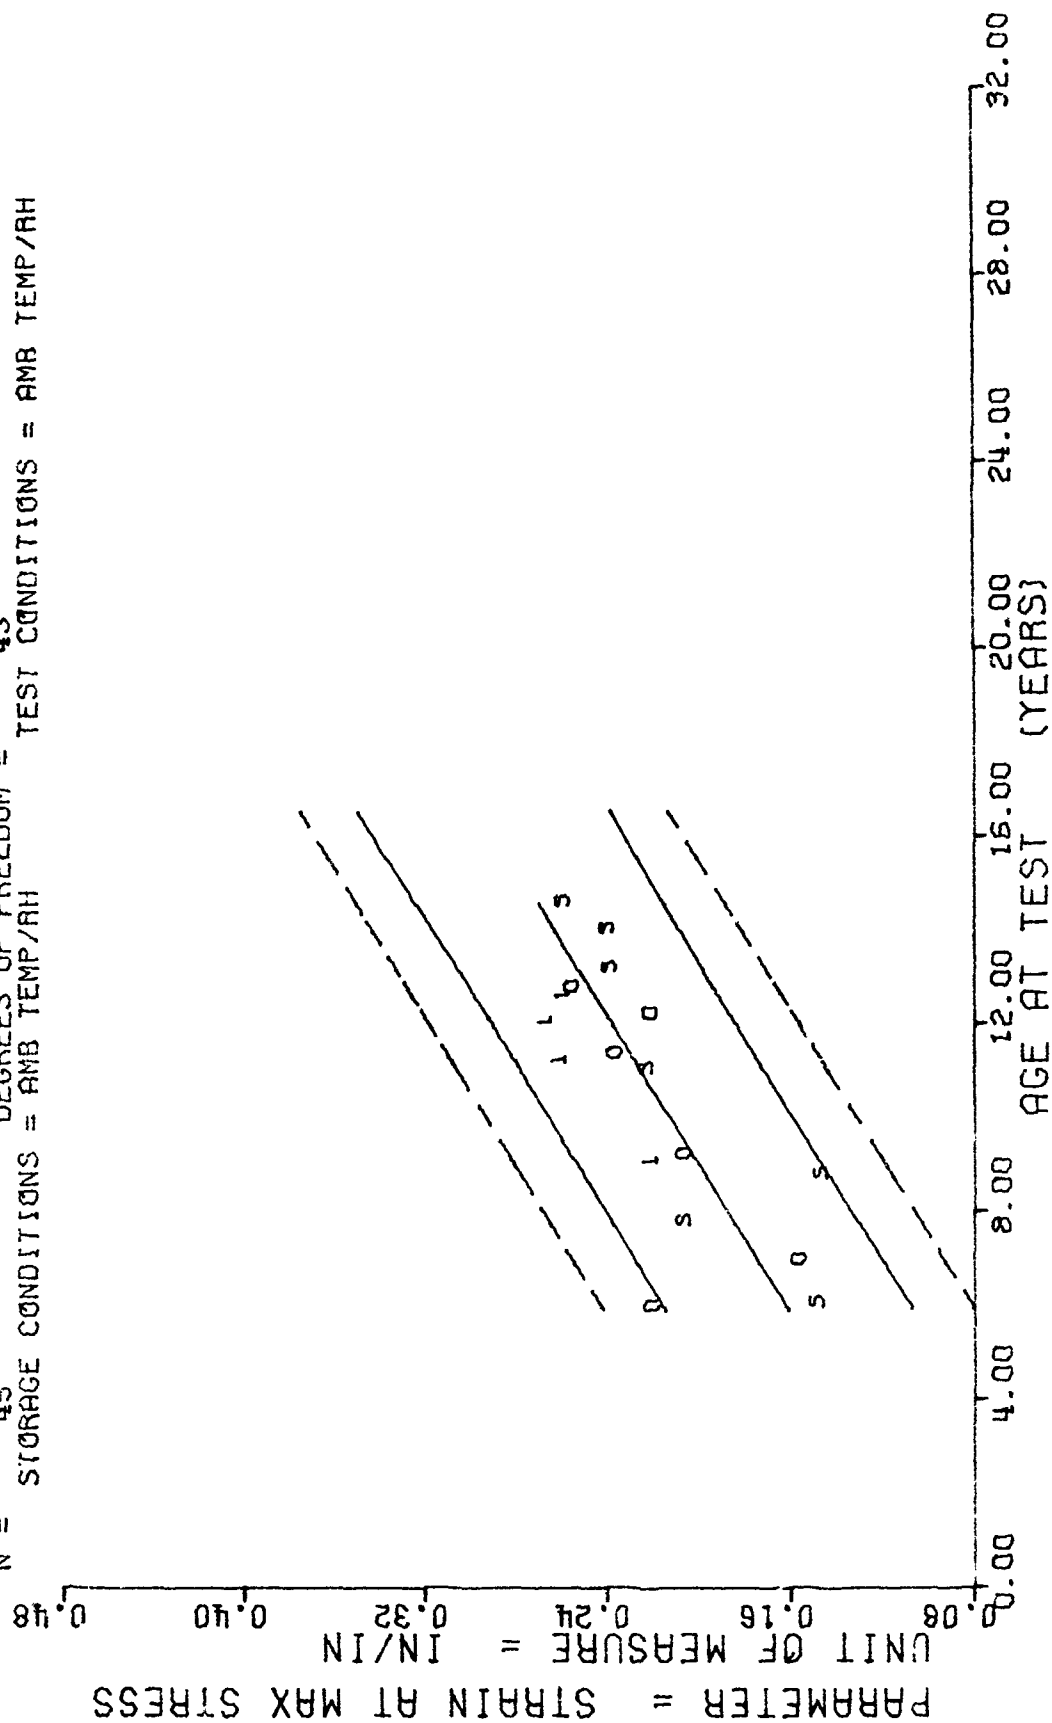

DISSECTED TP-H1011, H.R. 101AXIAL CHS=1750 IN/MIN, 600 PSI, STRAIN MAX STRESS

Figure 16

$Y = ((+5.3805176E+02) + (+5.0163470E-01) * X)$
 $F = +5.3886317E+00$ SIGNIFICANCE OF F = SIGNIFICANT $G = +5.3197150E+01$
 $R = +3.3370874E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S = +2.1609679E-01$
 $t = +2.3213426E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_t = +5.0727450E+01$
 $N = 45$ DEGREES OF FREEDOM = 43
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH


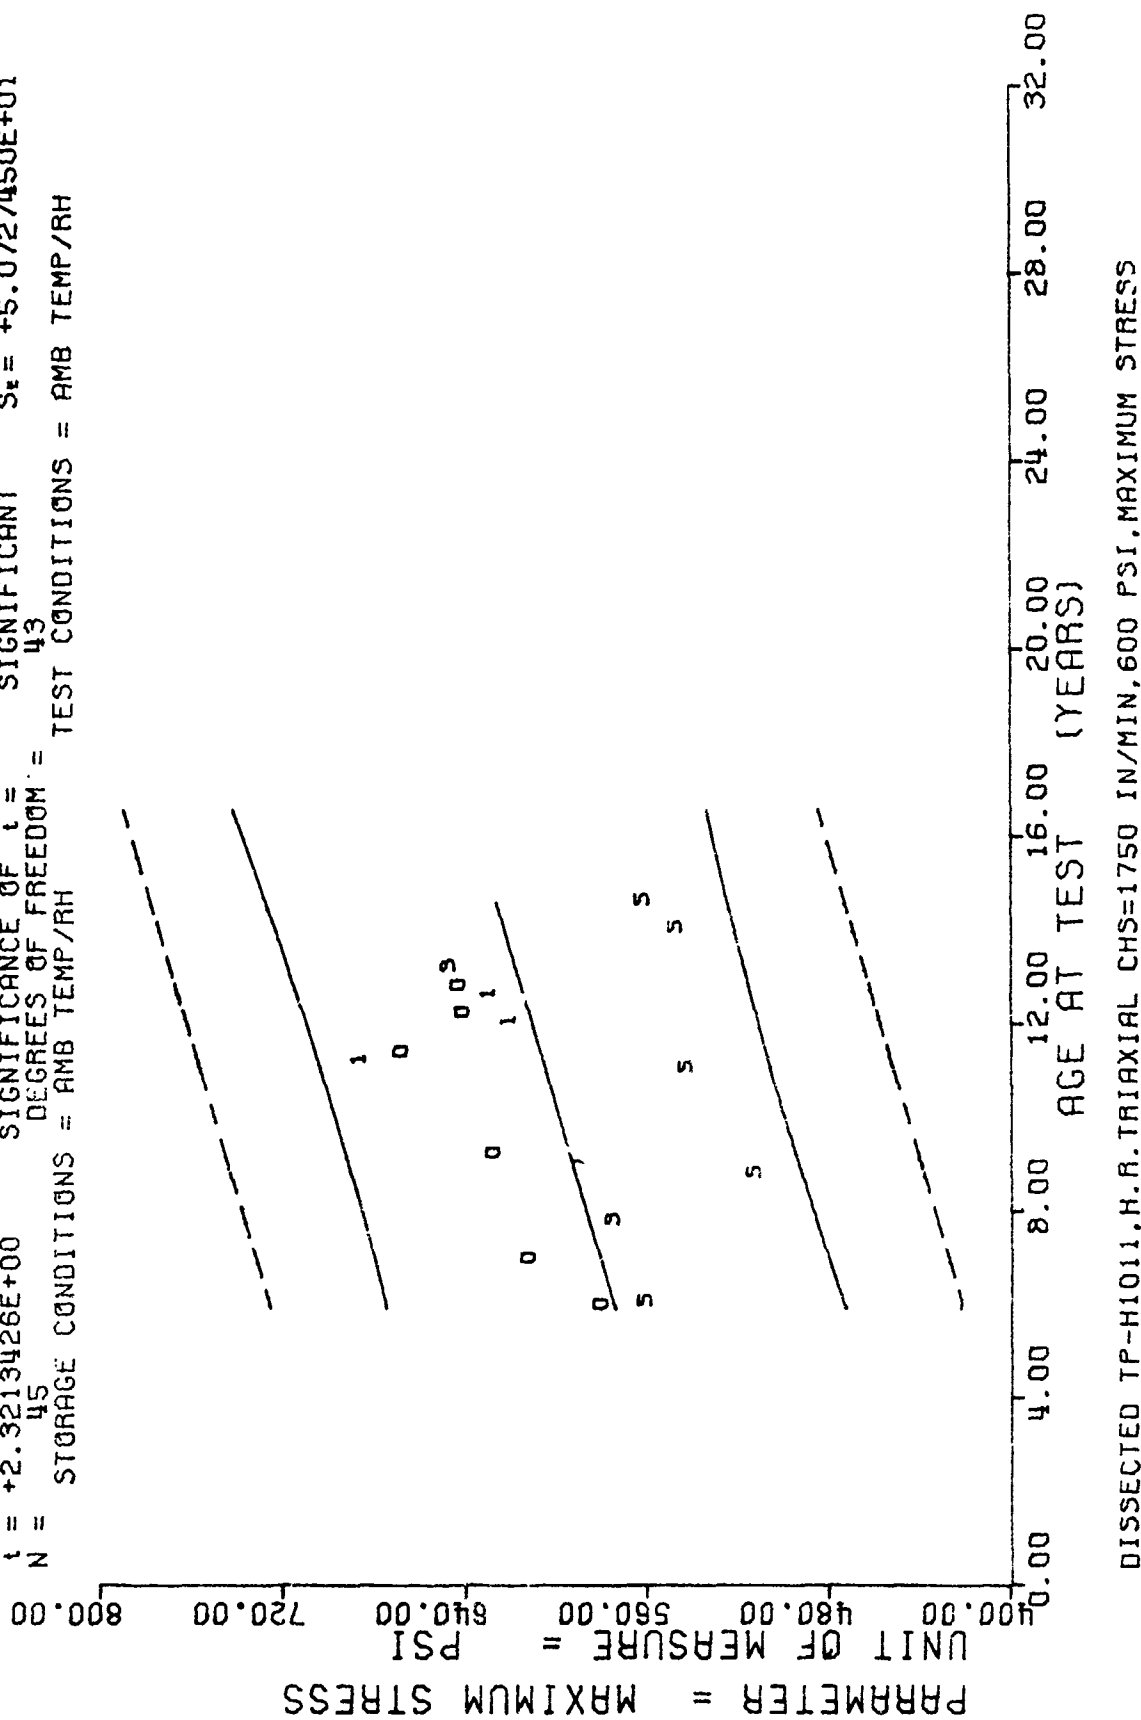


Figure 17


$F = +3.1872358E+01$ SIGNIFICANCE OF F = SIGNIFICANT $\sigma_t = +3.9199704E-02$
 $R = +6.5244866E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_e = +1.2801287E-04$
 $t = +5.6455608E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_t = +3.0050269E-02$
 $N = 45$ DEGREES OF FREEDOM = 43
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

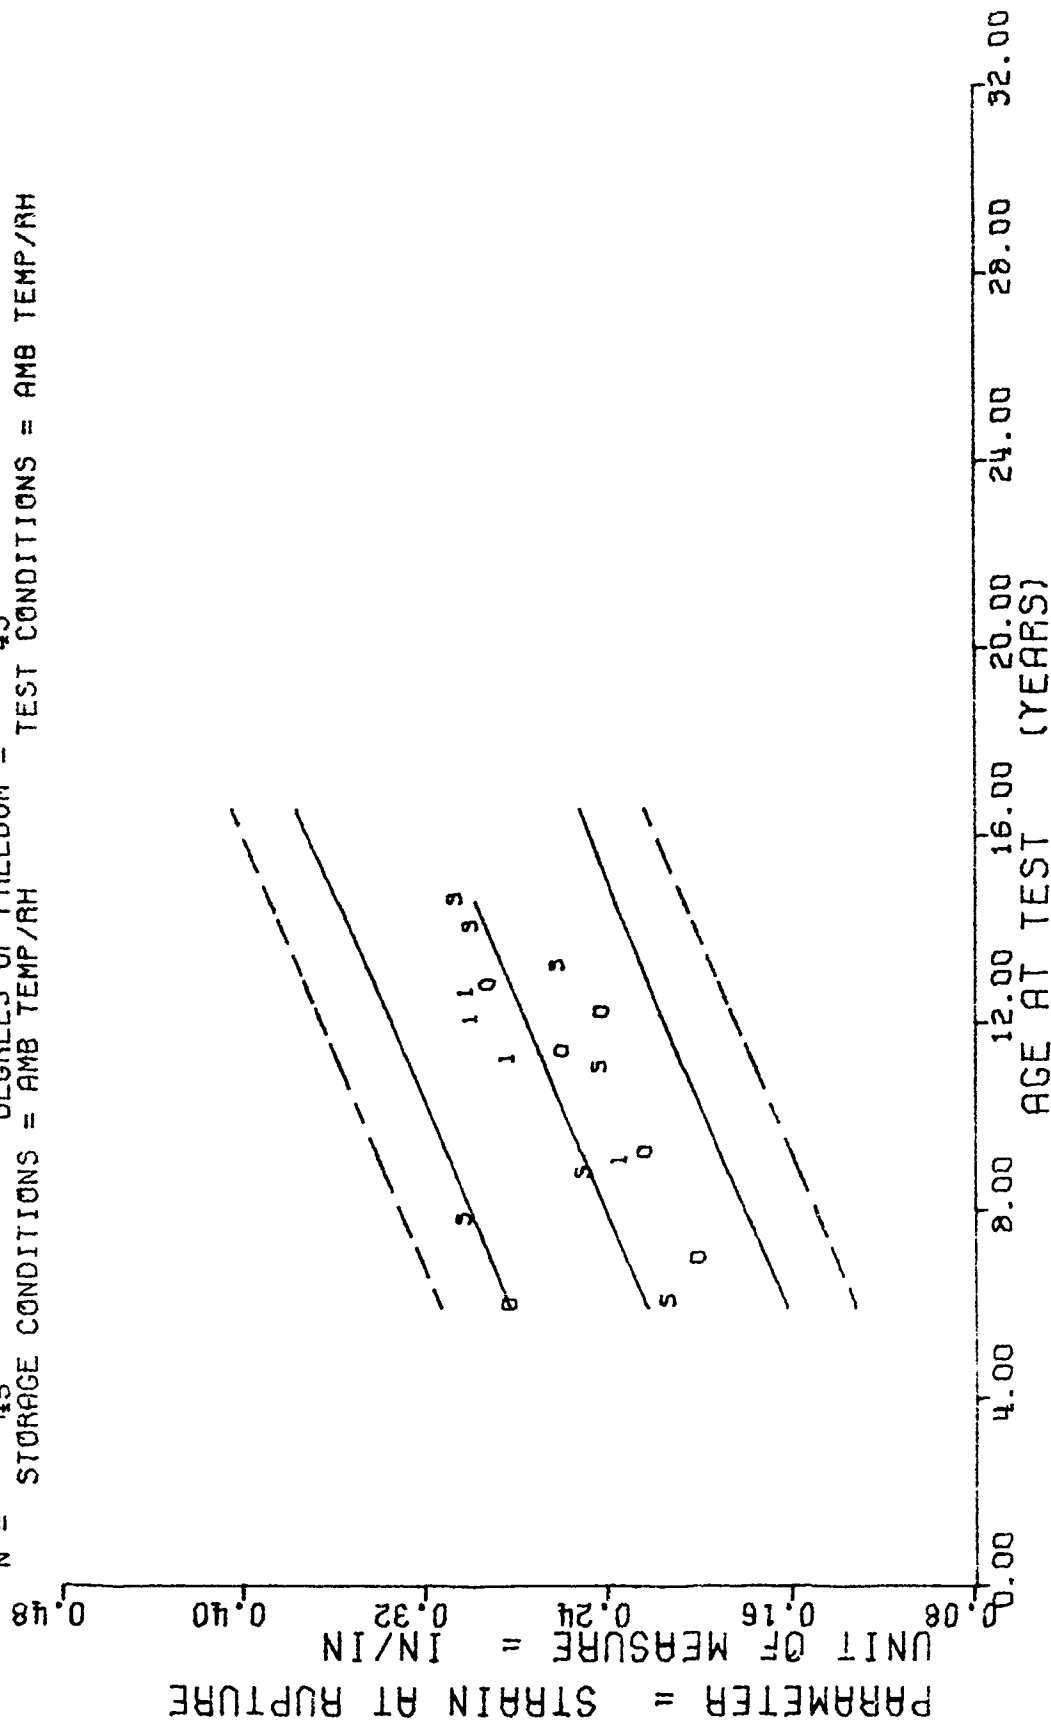

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN. 600 PSI, STRAIN AT RUPTURE

Figure 18


$Y = ((+4.8798314E+02) + (+7.3455714E-01) * X)$
 $F = +1.0378497E+01$ SIGNIFICANCE OF F = SIGNIFICANT $\alpha = +5.8953540E+01$
 $R = +4.4094464E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_a = +2.2801233E-01$
 $t = +3.2215675E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_e = +5.3524554E+01$
 $N = 45$ DEGREES OF FREEDOM = 43
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

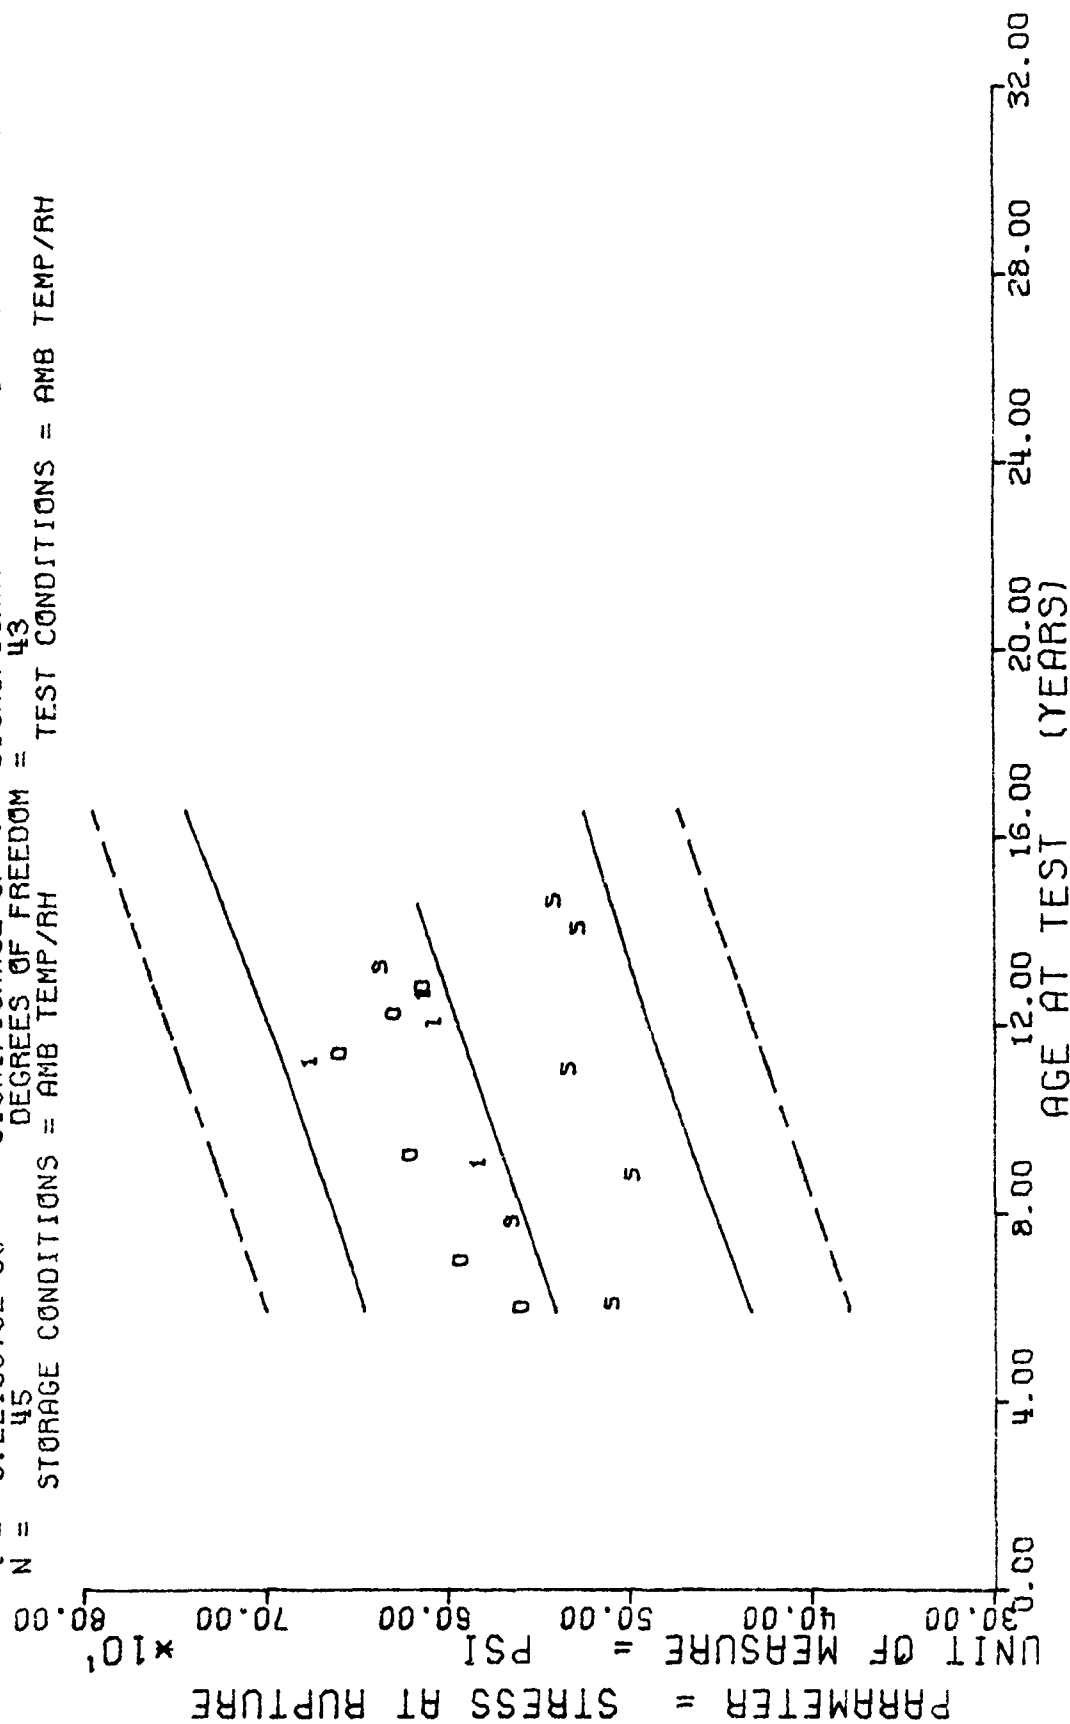

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, STRESS AT RUPTURE

Figure 19

$F = +3.3107249E+01$ SIGNIFICANCE OF F = $(-3.2998736E+01) \times X$ $\sigma_f = +1.7705865E+03$
 $R = -6.5955123E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_e = +5.7350309E+00$
 $t = +5.7538899E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_x = +1.3402647E+03$
 $N = 45$ DEGREES OF FREEDOM = 43
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

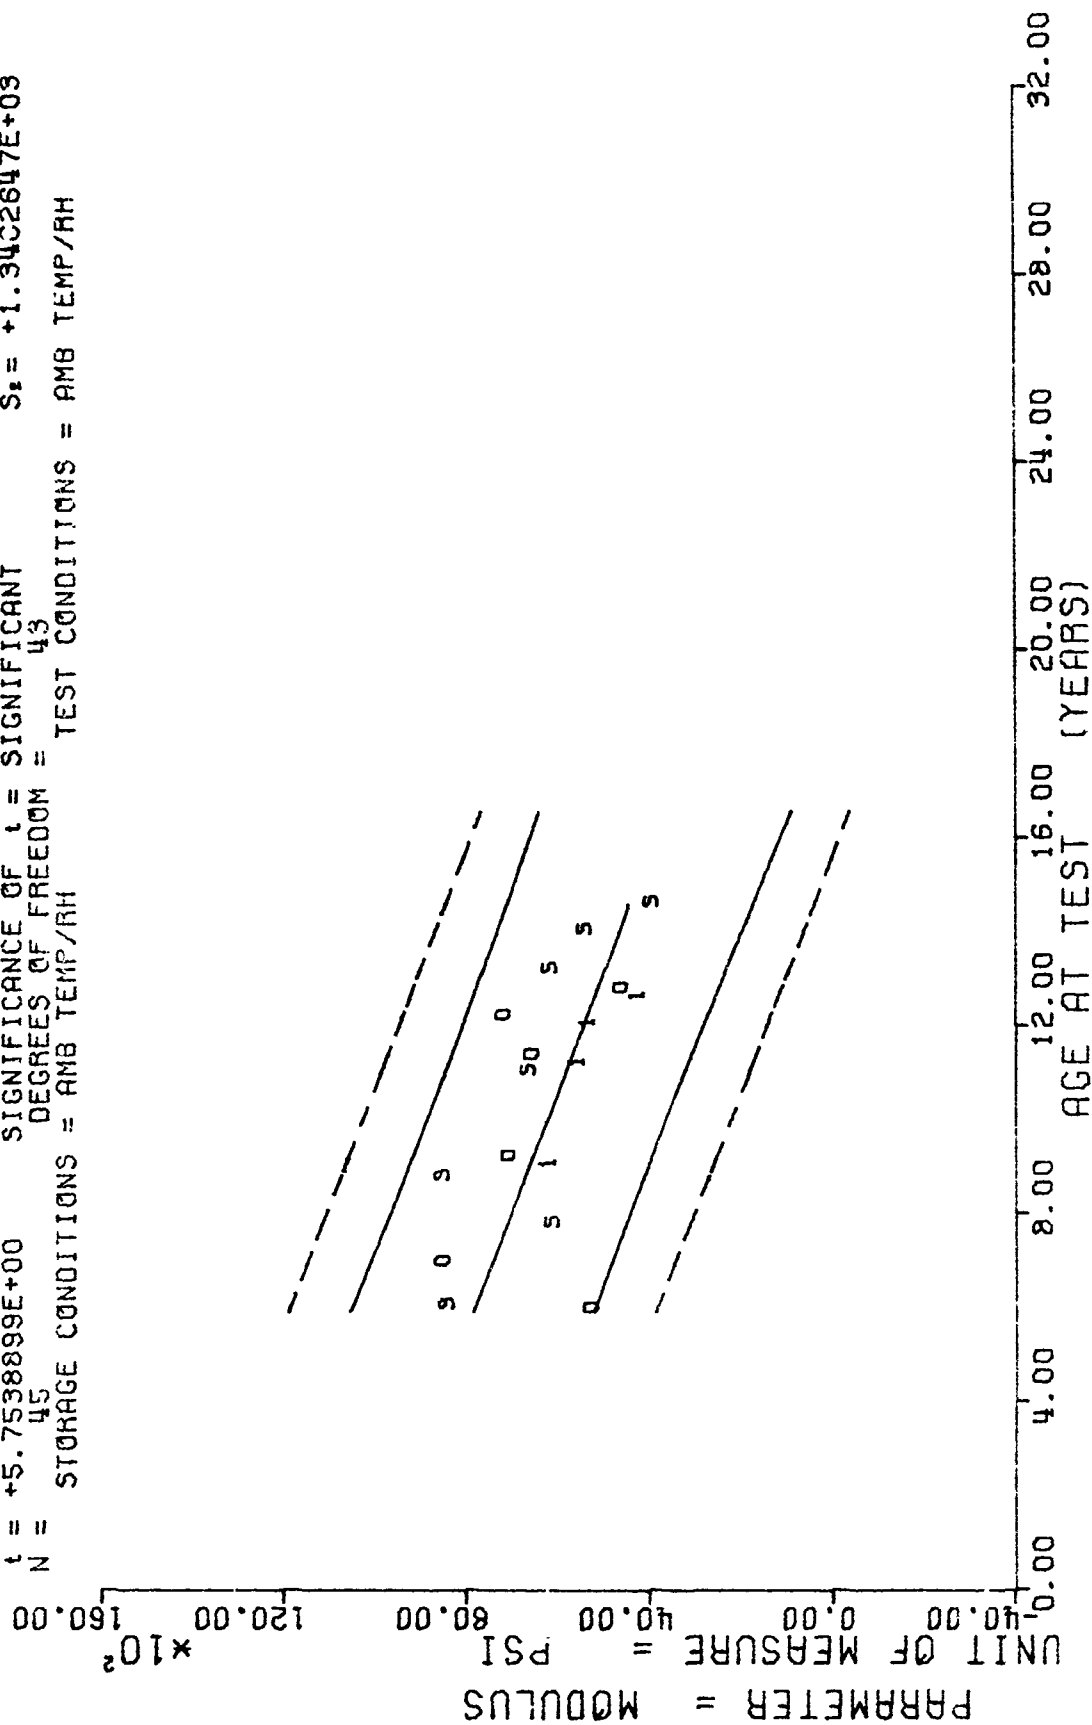

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, MODULUS

Figure 20


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
80.0	27
94.0	2
104.0	10
113.0	12
116.0	12
141.0	11
154.0	9
156.0	22
166.0	9
178.0	8
189.0	11

CASEBOND TE ISILE, STAGE 1 DISSECTED, CHS 0.2, CSA 0.75

This sample size summary is applicable to figure 21

$Y = ((+1.2658054E+02) + (-1.8179137E-01) * X)$
 $F = +2.0184099E+01$ SIGNIFICANCE OF F = SIGNIFICANT $G = +1.7965334E+01$
 $R = -3.6538576E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +4.0463979E-02$
 $t = +4.4926717E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_2 = +1.6786850E+01$
 $N = 133$ DEGREES OF FREEDOM = 131
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

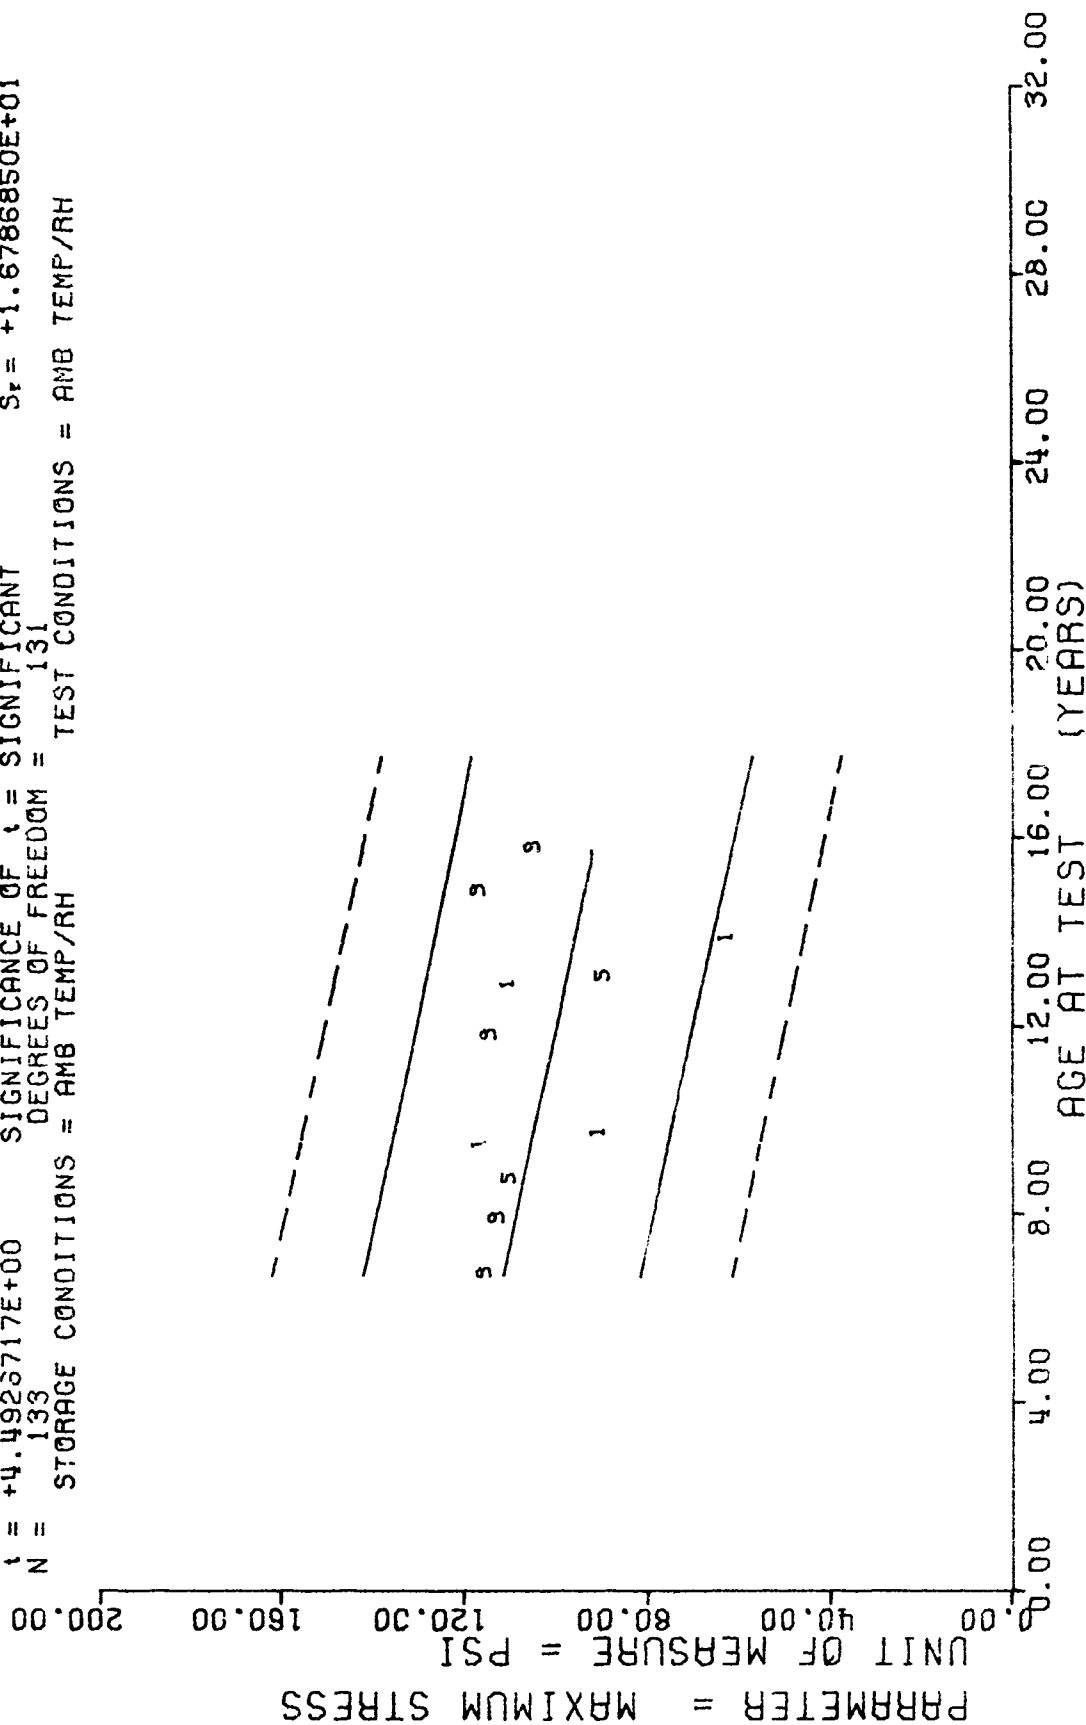

CASEBOND TENSILE, STAGE 1 DISSECTED, CHS 0.2, CSA 0.75

Figure 21


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
132.0	2
134.0	2
144.0	2
146.0	2
149.0	2
151.0	4
153.0	3
157.0	1
160.0	2
167.0	4
168.0	3
175.0	2
176.0	1

DISSECTED MOTOR TP-H1011.CREEP 10 LB LCAD.COMPLIANCE AT 10 SEC.

This sample size summary is applicable to figures 22 thru 24


$F = +3.8184801E+00$
 $R = -2.7411602E-01$
 $t = +1.9540931E+00$
 $N = 49$
 $Y = \{ (+1.4473901E-03) + (-2.5894067E-06) \} \times X$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 47
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

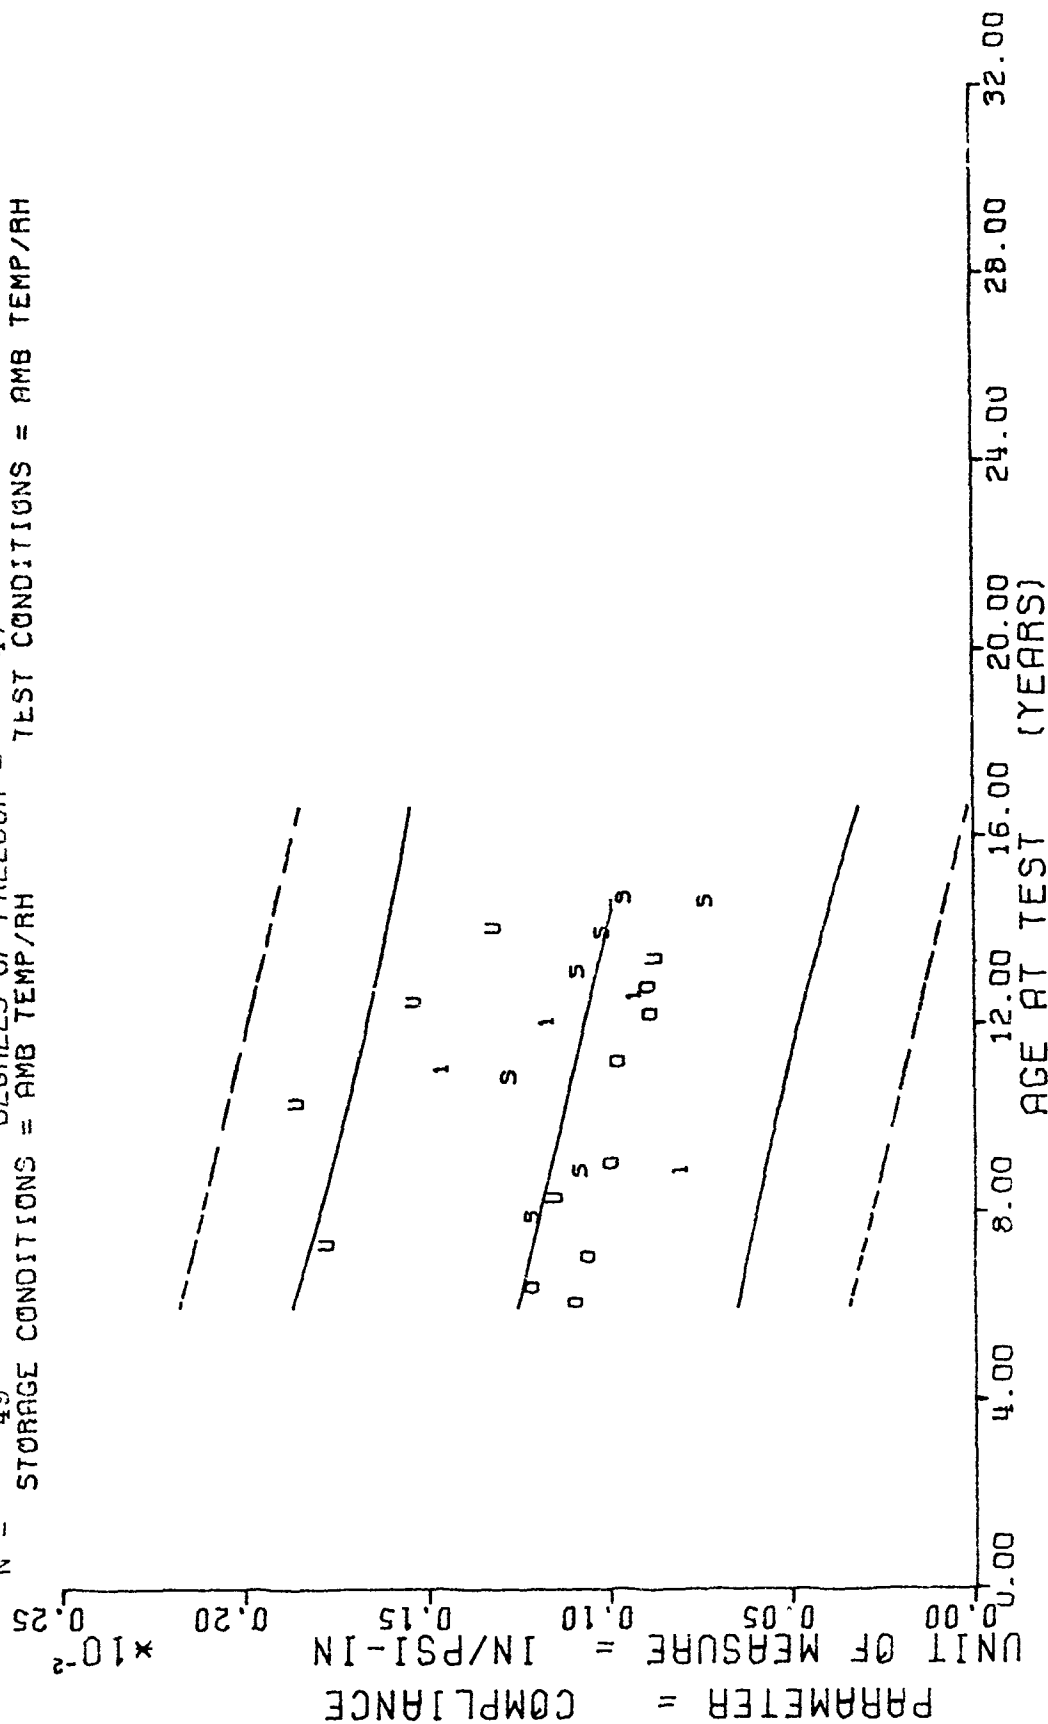

DISSECTED MOTOR 7P-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10 SEC.

Figure 22


$F = +6.2916814E+00$
 $R = -3.4360039E-01$
 $t = +2.5083224E+00$
 $N = 49$
 $Y = \{ (+1.7301439E-03) + (-3.5999771E-06) * X \}$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 47
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

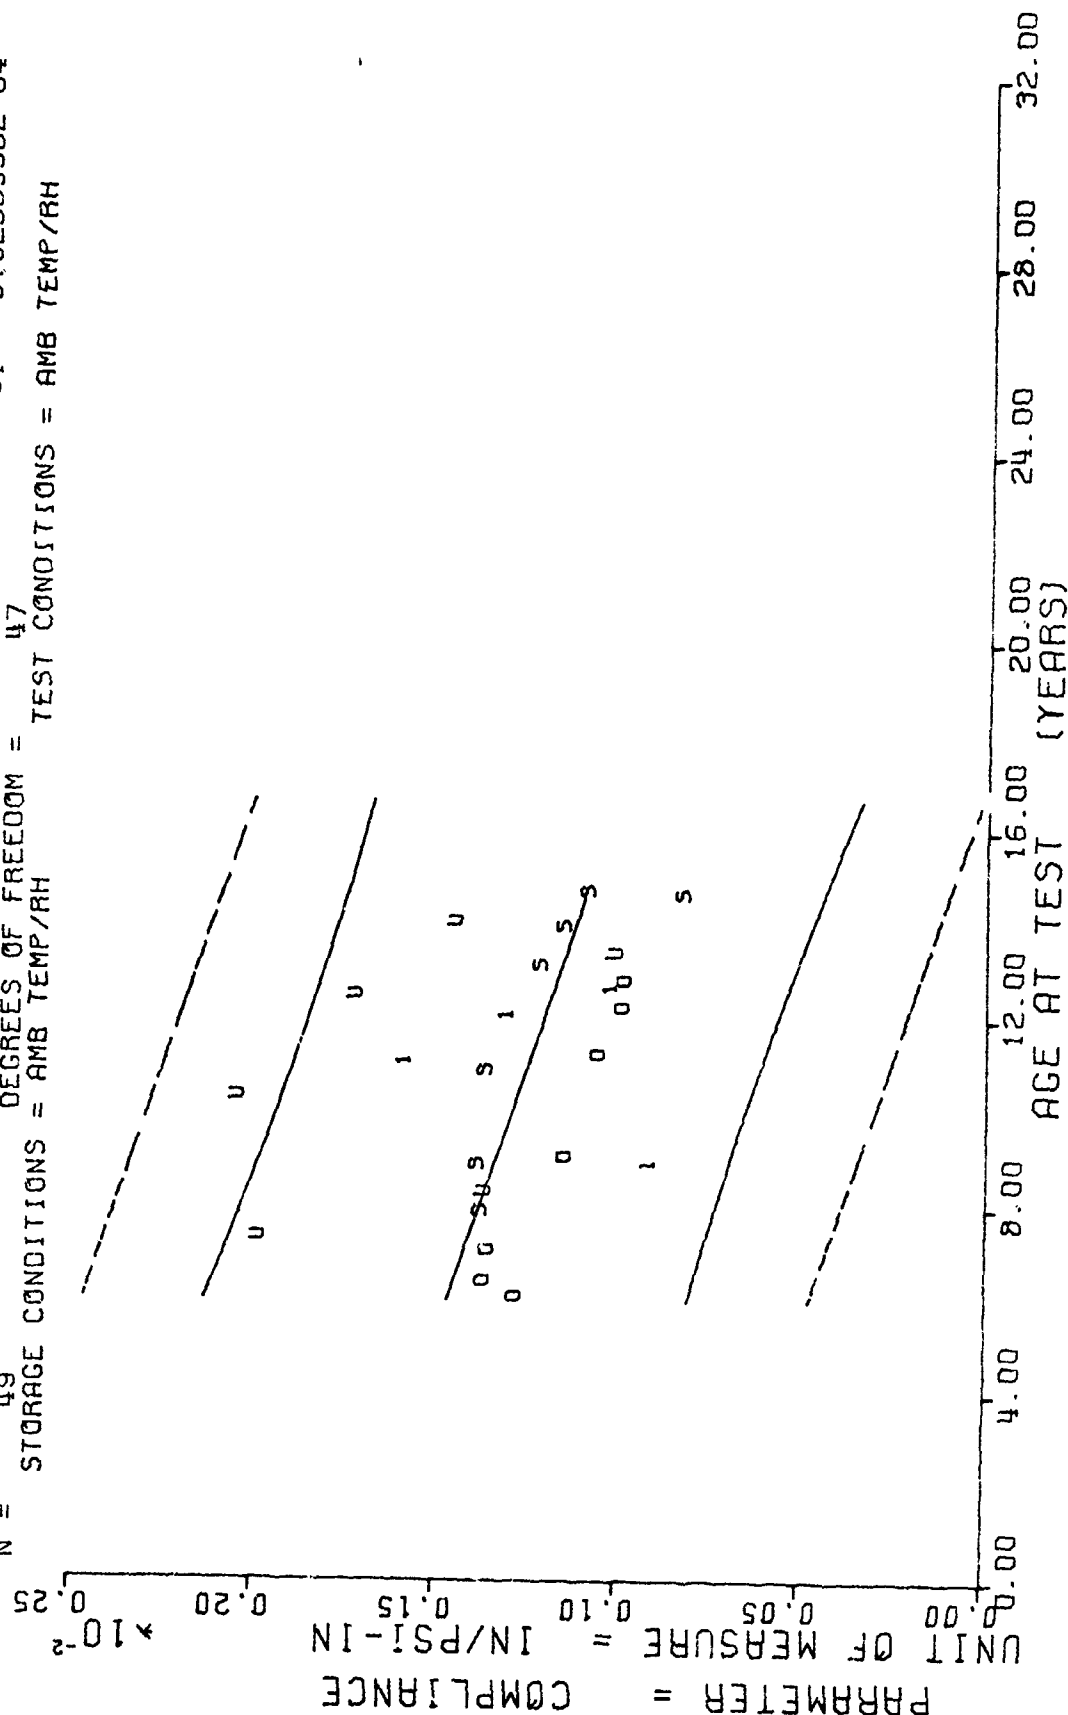

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 20 SEC.

Figure 23

$F = +1.1099330E+00$ SIGNIFICANCE OF $F = \{ -2.3740268E-06 \} * X$ $\sigma_f = +5.2246464E-04$
 $R = -1.5189063E-01$ SIGNIFICANCE OF $R =$ NOT SIGNIFICANT $S_e = +2.2533945E-06$
 $t = +1.0535335E+00$ SIGNIFICANCE OF $t =$ NOT SIGNIFICANT $S_f = +5.2186737E-04$
 $N = 49$ DEGREES OF FREEDOM = 47
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

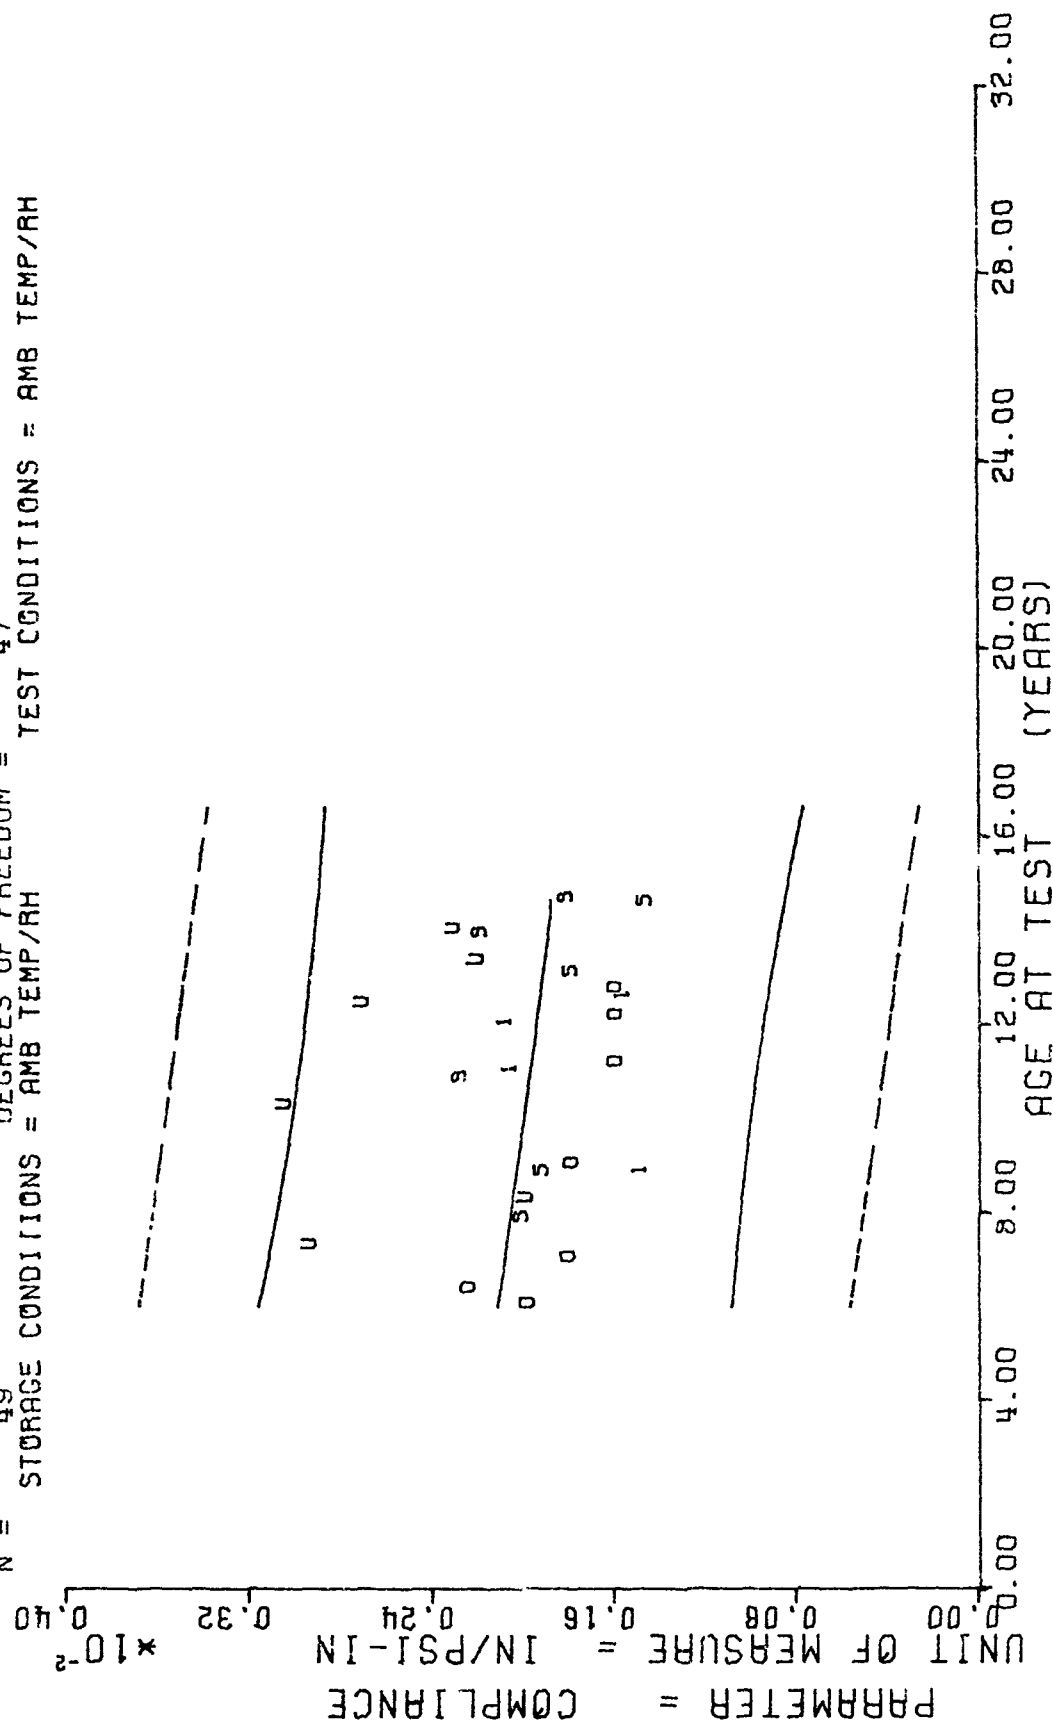

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 1000 SEC.

Figure 24


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	2
108.0	1
123.0	1
130.0	1
151.0	1

DISSECTED MOTOR IP-H1011.CREEP 10 LB LOAD, COMPLIANCE AT 10.000 SEC.

This sample size summary is applicable to figure 25

$Y = ((+2.5549900E-03) + (+2.9741959E-06) * X)$
 F = +2.2754847E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_y = +5.5222611E-04$
 R = +1.1173077E-01 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_e = +6.2349448E-05$
 t = +4.7702040E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_e = +5.6380589E-04$
 N = 20 DEGREES OF FREEDOM = 18
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

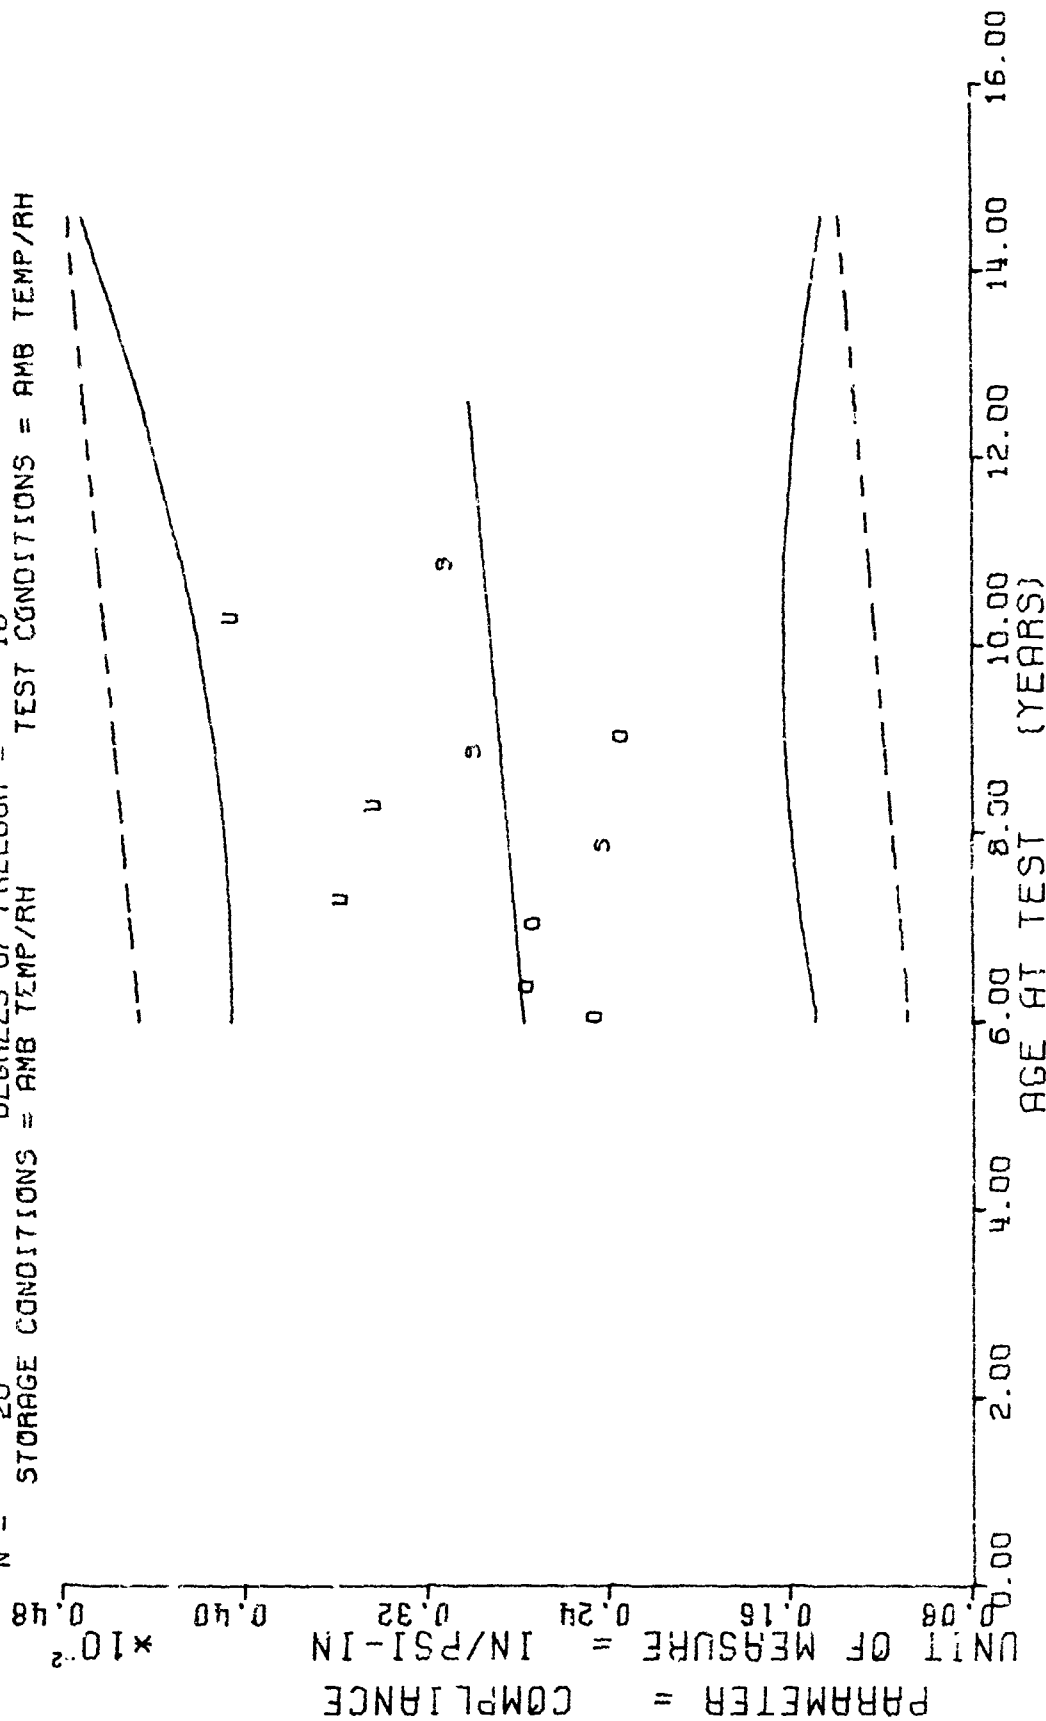

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10,000 SEC.

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
132.0	2
134.0	2
144.0	2
146.0	2
149.0	2
151.0	2
153.0	3
157.0	2
160.0	2
167.0	1
168.0	3
175.0	2

DISSECTED MOTOR TP-H1011, CREEP 12 LB LCAD, COMPLIANCE AT 10 SEC.

This sample size summary is applicable to figures 26 thru 28

$F = +2.5293750E+00$ SIGNIFICANCE OF $F = \{ +1.6812355E-03 \} + \{ -2.7715186E-06 \} \times X$
 $R = -2.3833252E-01$ SIGNIFICANCE OF $R =$ NOT SIGNIFICANT $G_1 = +3.8455817E-04$
 $t = +1.5904008E+00$ SIGNIFICANCE OF $t =$ NOT SIGNIFICANT $S_1 = +1.7426541E-06$
 $N = 44$ DEGREES OF FREEDOM = 42 $S_F = +3.7789659E-04$
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH


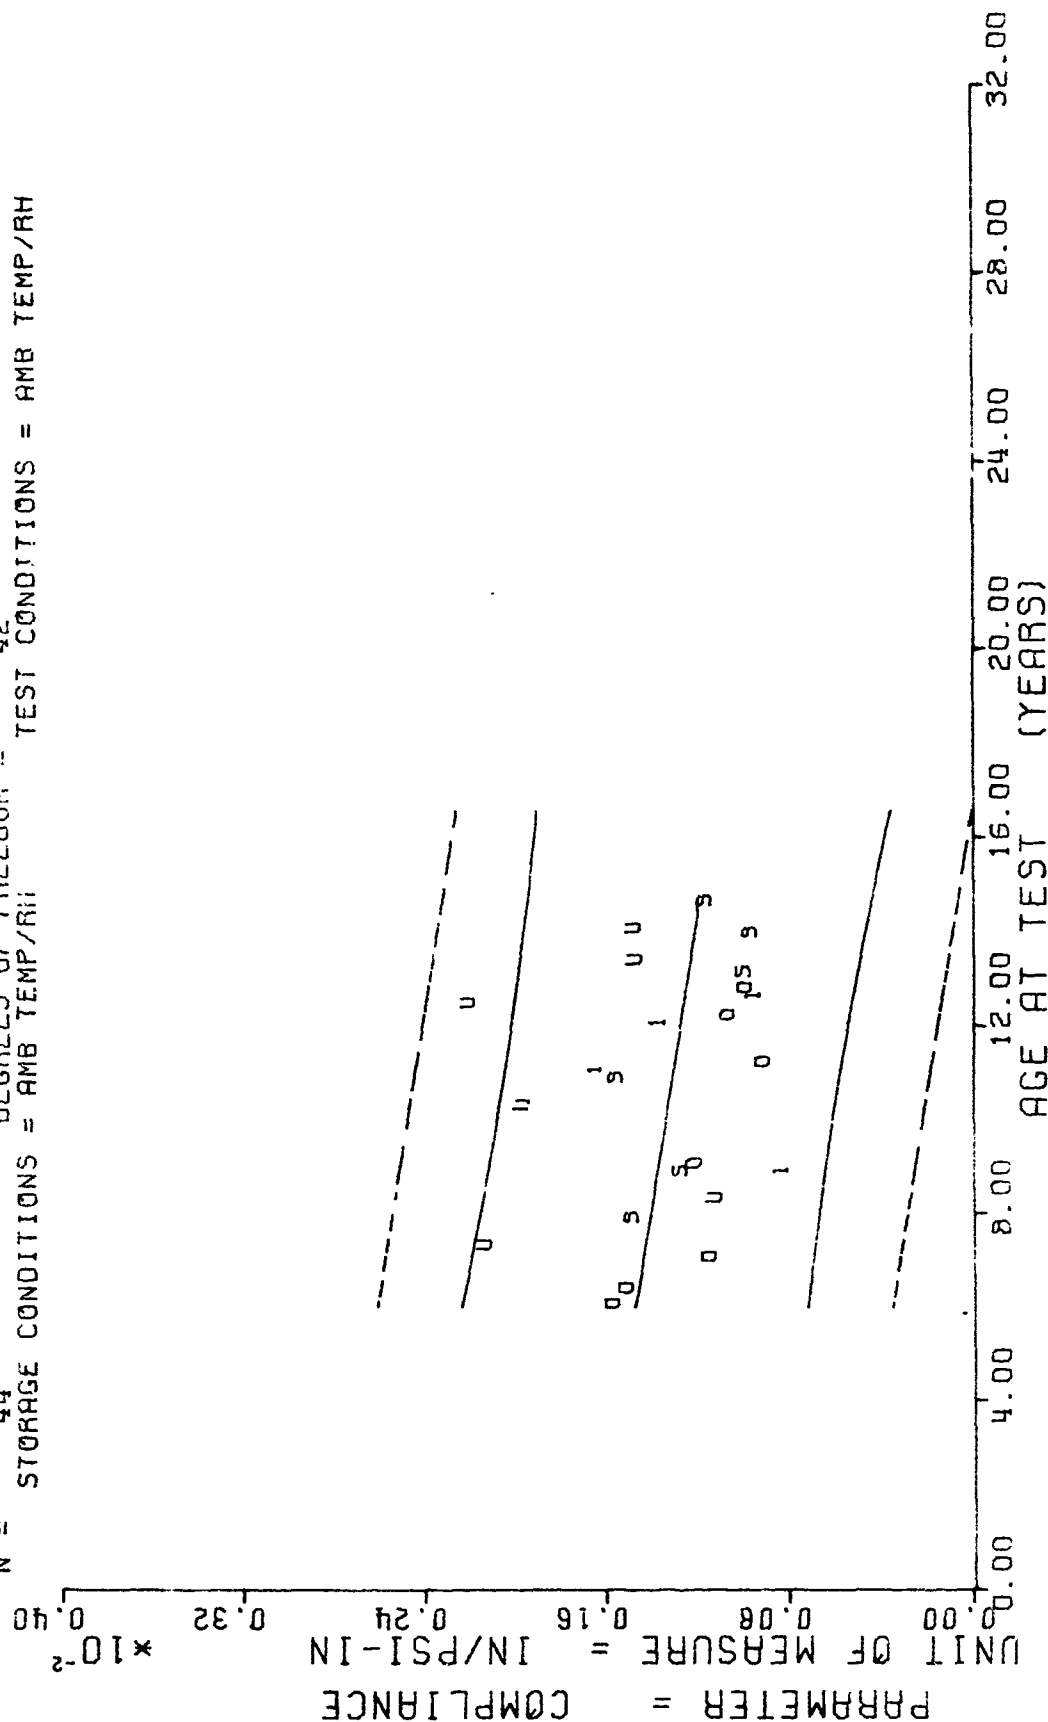


Figure 26


$F = +3.2736850E+00$
 $R = -2.6890292E-01$
 $t = +1.8093327E+00$
 $N = 44$
 $Y = ((+1.9651932E-03) + (-3.4966108E-06)) \times X$
 SIGNIFICANCE OF $F =$ NOT SIGNIFICANT
 SIGNIFICANCE OF $R =$ NOT SIGNIFICANT
 SIGNIFICANCE OF $t =$ NOT SIGNIFICANT
 DEGREES OF FREEDOM = 42
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

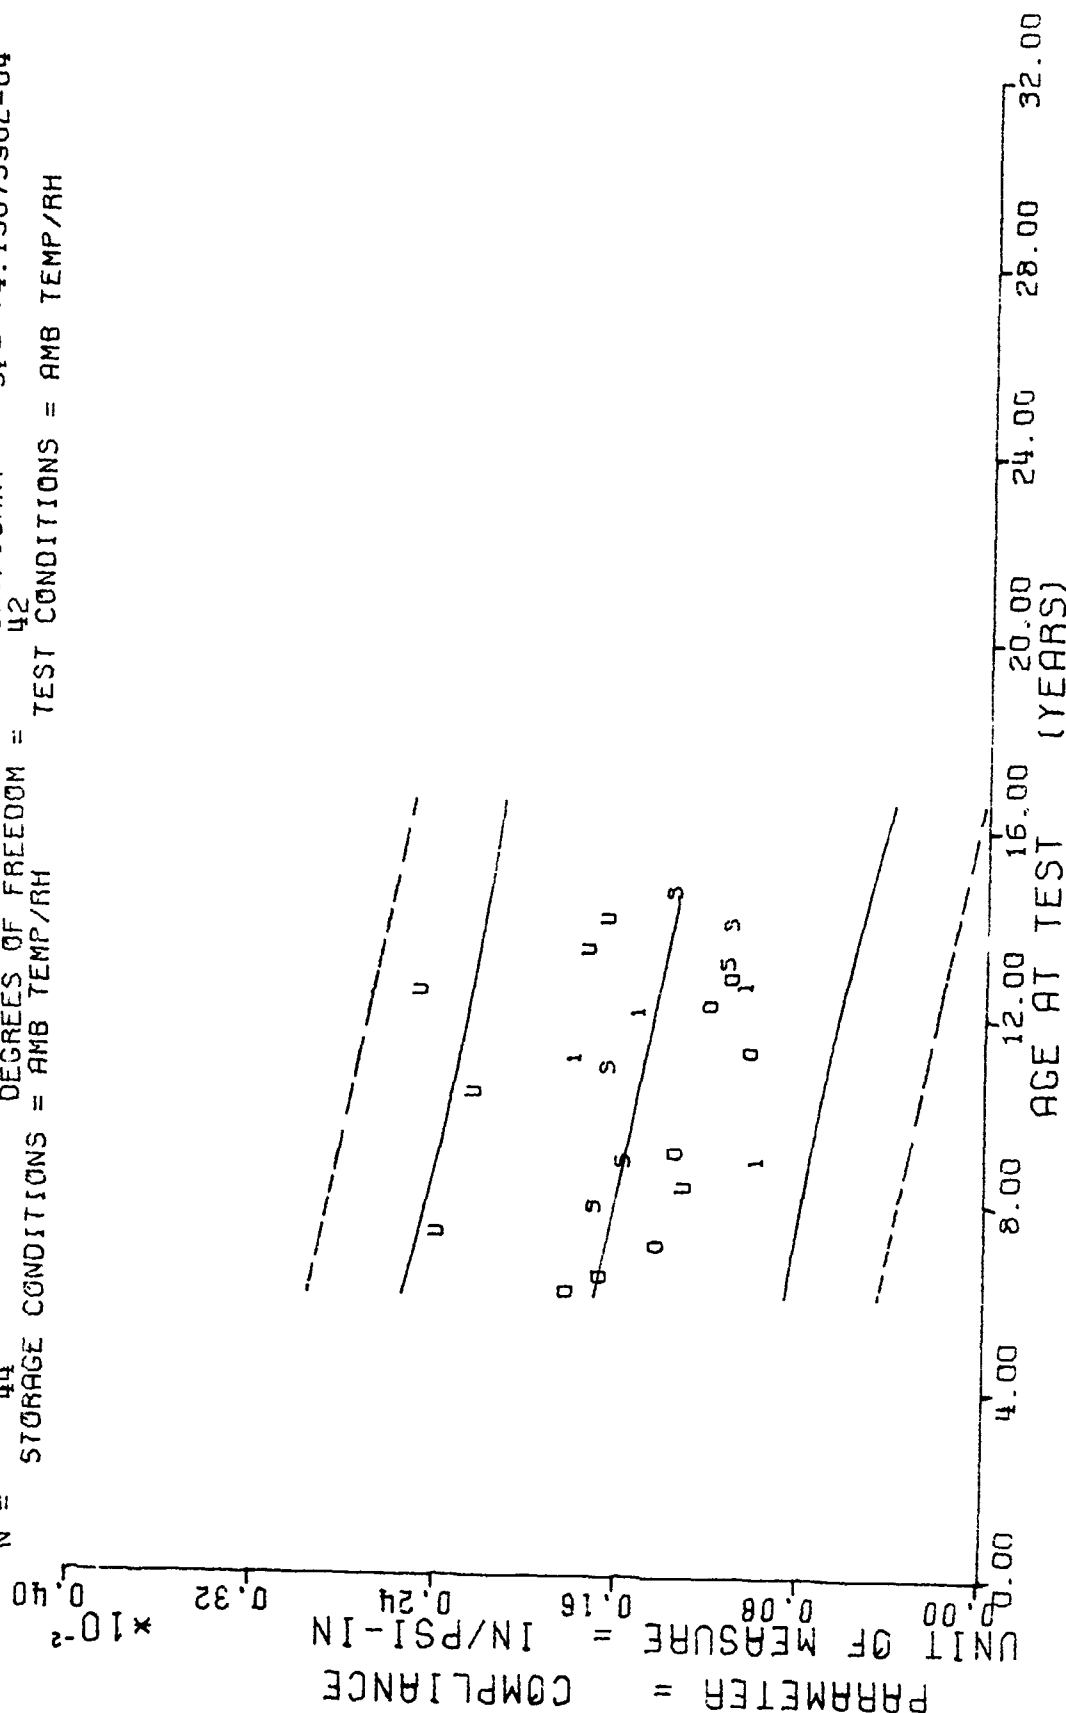

DISSECTED MOTOR TP-H1011, CREEP 12 LB LOAD, COMPLIANCE AT 20 SEC.

Figure 27

$t = +2.0963788E+00$
 $R = -2.2315802E-01$
 $t = +1.4478877E+00$
 $N = 42$
 STORAGE CONDITIONS = AMB TEMP/RH
 $f = ((+3.0045415E-03) + (-4.4802120E-06) \times X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 40
 $\sigma = +6.6752842E-04$
 $S_e = +3.0943090E-06$
 $S_f = +6.5877835E-04$
 TEST CONDITIONS = AMB TEMP/RH

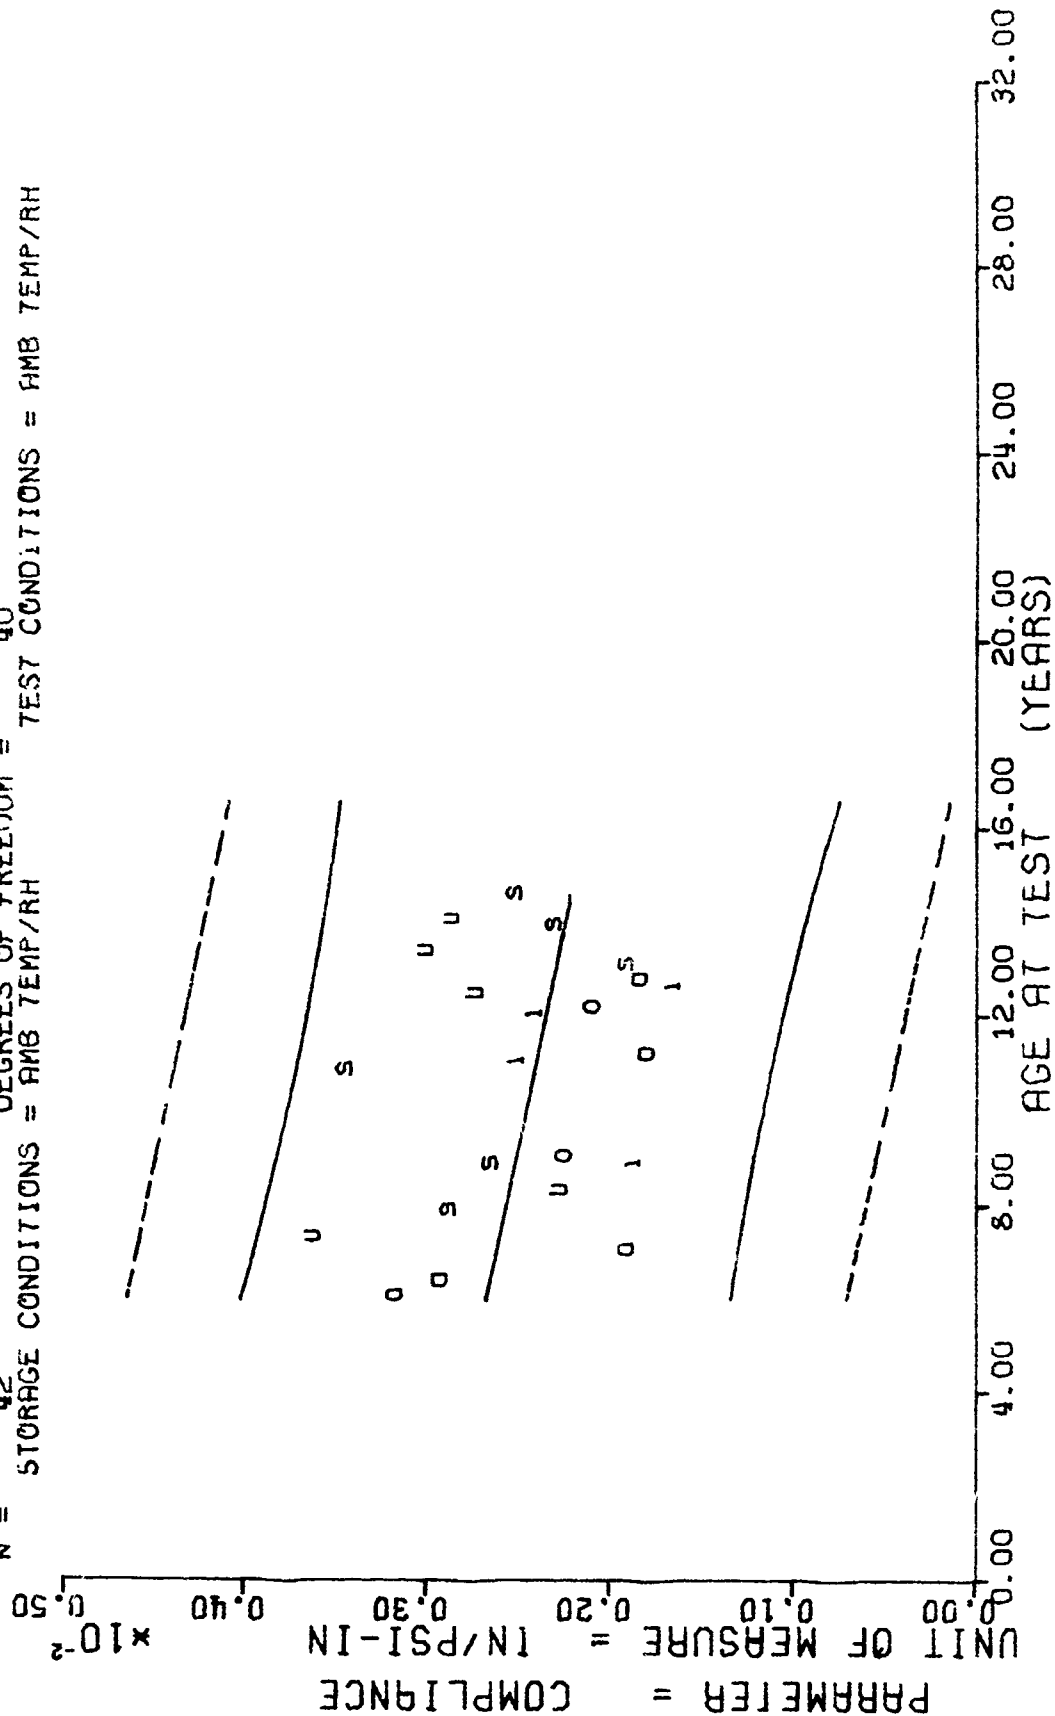

DISSECTED MOTOR TP-H1011, CREEP 12 LB LOAD, COMPLIANCE AT 1000 SEC.

Figure 28


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
84.0	2
87.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1

TP-H1011 DISSECTED MOTORS. CREEP. % STRAIN AT RUPTURE. 12 LB LCAD

This sample size summary is applicable to figure 29

$Y = ((+1.9802813E+01) + (+3.2539982E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_r = +1.7895953E+00$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_a = +3.6716661E-02$
 SIGNIFICANCE OF I = NOT SIGNIFICANT $S_i = +1.8073090E+00$
 DEGREES OF FREEDOM = 10
 N = 12
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TMP/RH 12 LB

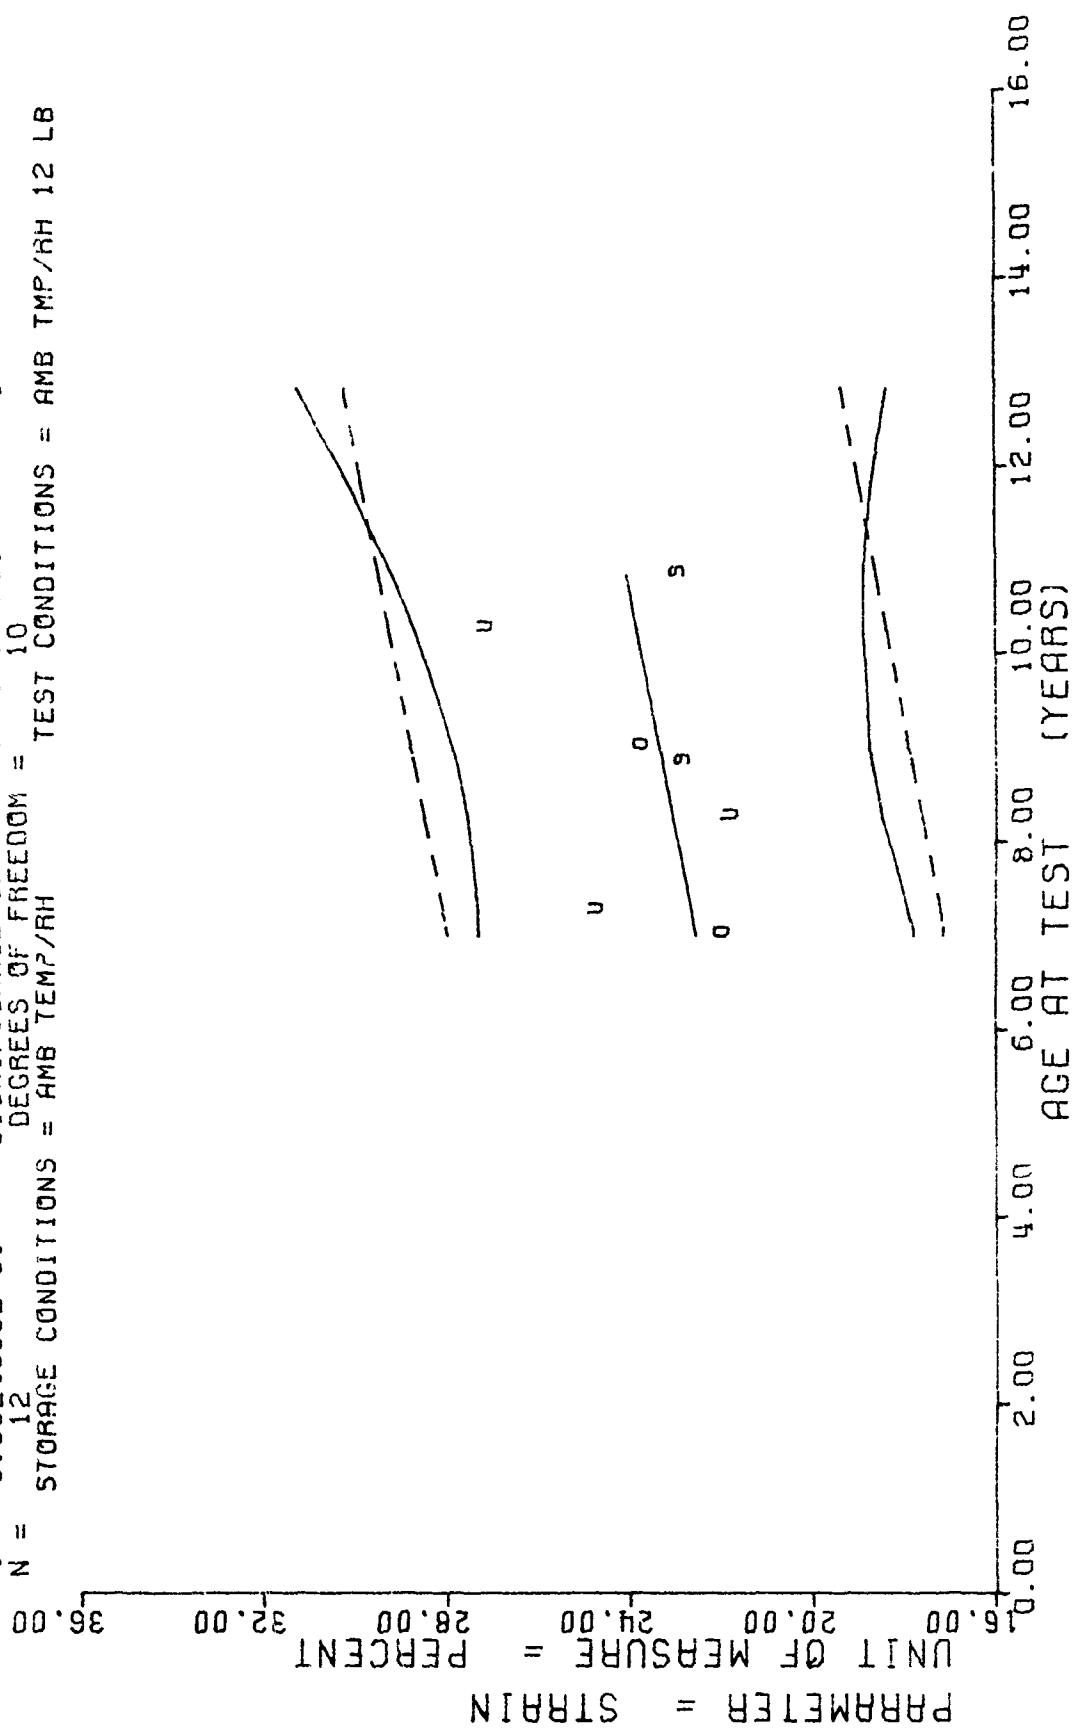

TP-H1011 DISORDERED MOTORS, CREEP, % STRAIN AT RUPTURE, 12 LB LOAD

*** SAMPLE SIZE SUMMARY ***


AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
57.0	3	166.0	3
60.0	3	168.0	9
73.0	3	175.0	3
82.0	3	183.0	3
84.0	3	190.0	3
88.0	3		
95.0	4		
99.0	3		
106.0	5		
108.0	3		
116.0	3		
118.0	3		
123.0	3		
130.0	3		
132.0	3		
133.0	3		
134.0	3		
140.0	3		
144.0	4		
145.0	3		
150.0	3		
151.0	3		
153.0	3		
157.0	3		
160.0	3		

IP-H1011 DISSECTED MRS. STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 10 SEC

This sample size summary is applicable to figures 30 thru 33


$F = +7.3993930E-02$
 $R = +2.7328652E-02$
 $t = +2.7201825E-01$
 $N = 101$

$Y = ((+6.5193585E+02) + (+1.0936496E-01) \times X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 99
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

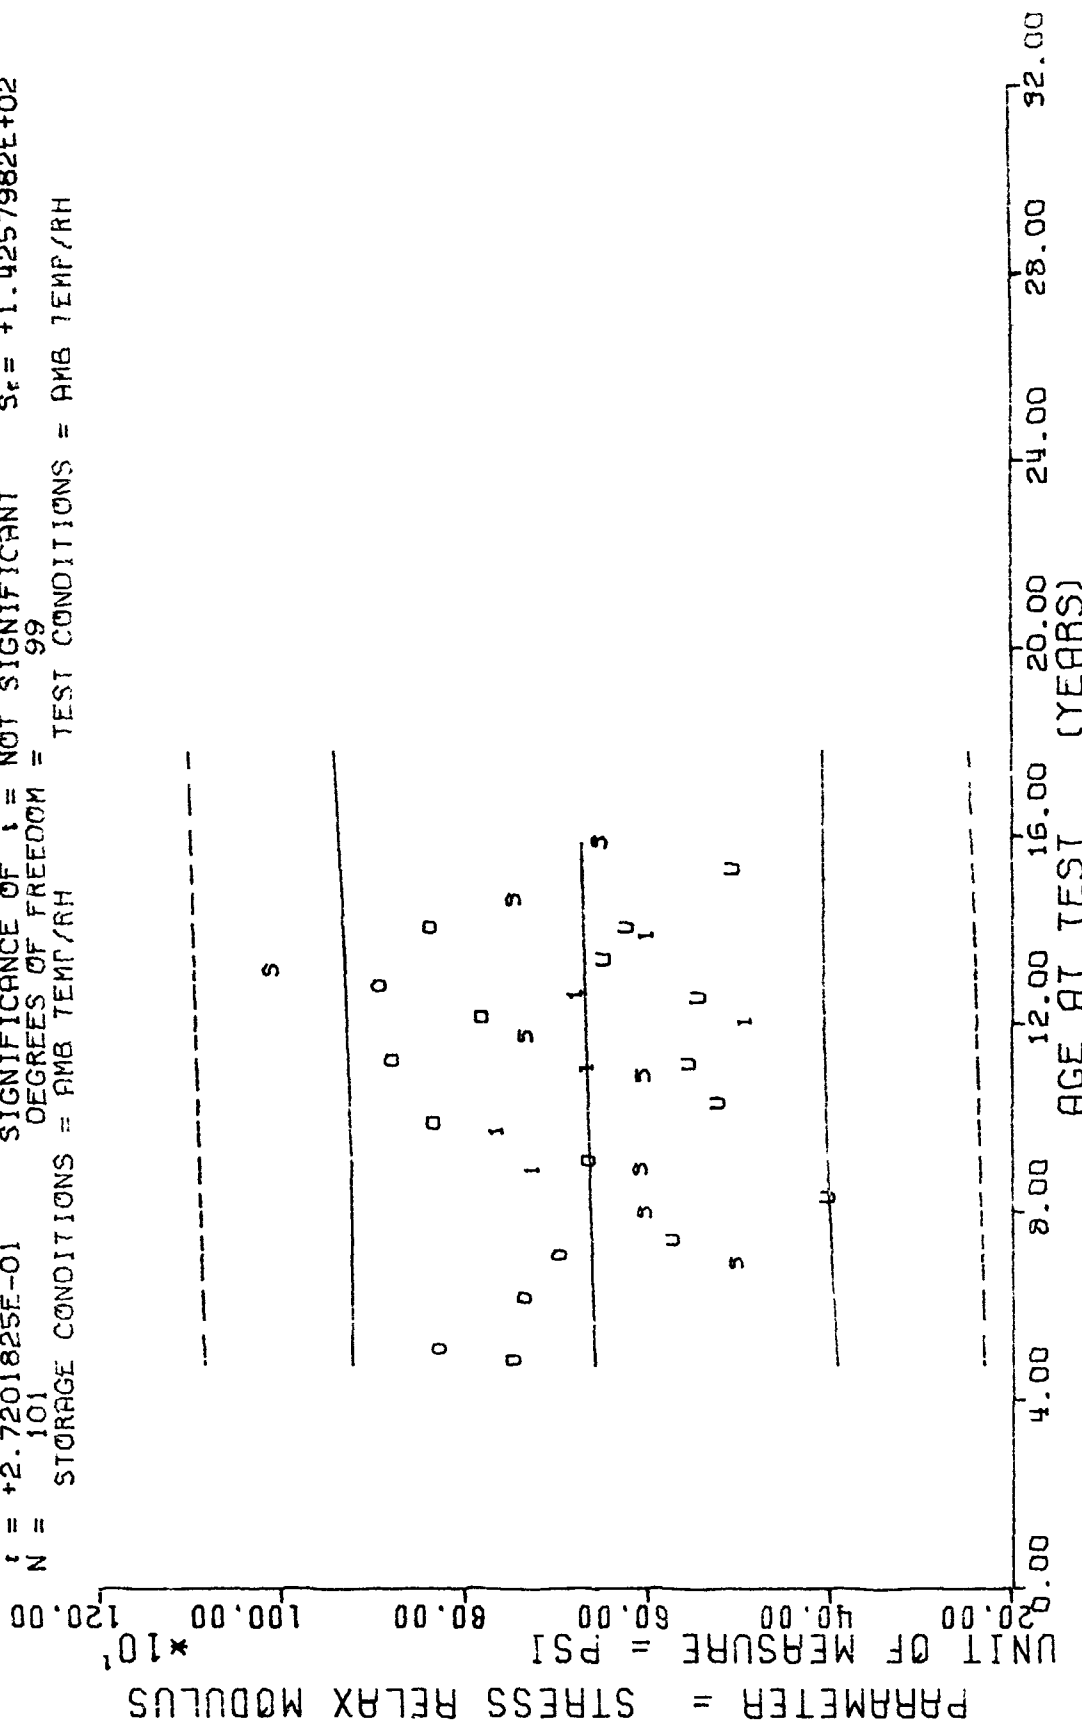

TP-H1011 DISSECTED MTRS, STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 10 SEC

F = +2.0198554E-02
 R = -1.4282303E-02
 t = +1.4212161E-01
 N = 101
 Y = ((+5.1906605E+02) + (-4.6577476E-02) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 99
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

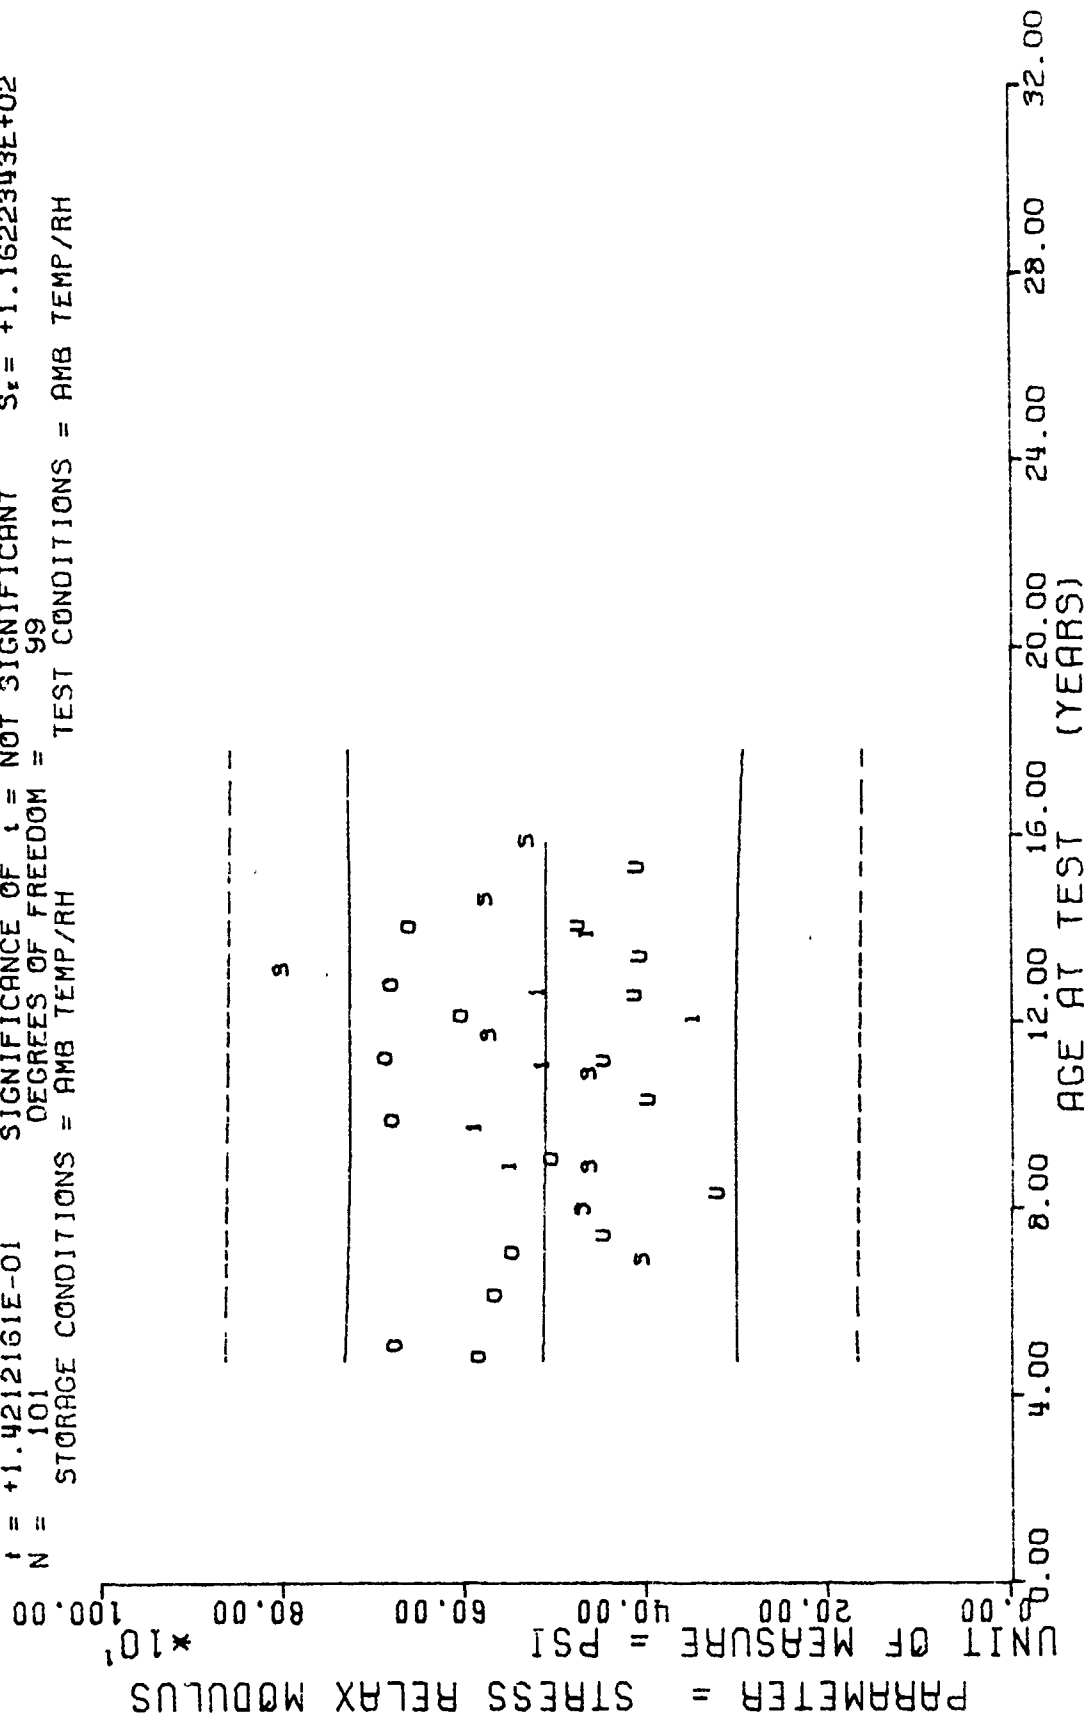


TP-H1011 DISSECTED MTRS. STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 50 SEC

$F = +2.8870337E-02$
 $R = -1.7074383E-02$
 $t = +1.6991273E-01$
 $N = 101$

$Y = ((+E.8275853E+02) + (-5.1409730E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 99

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

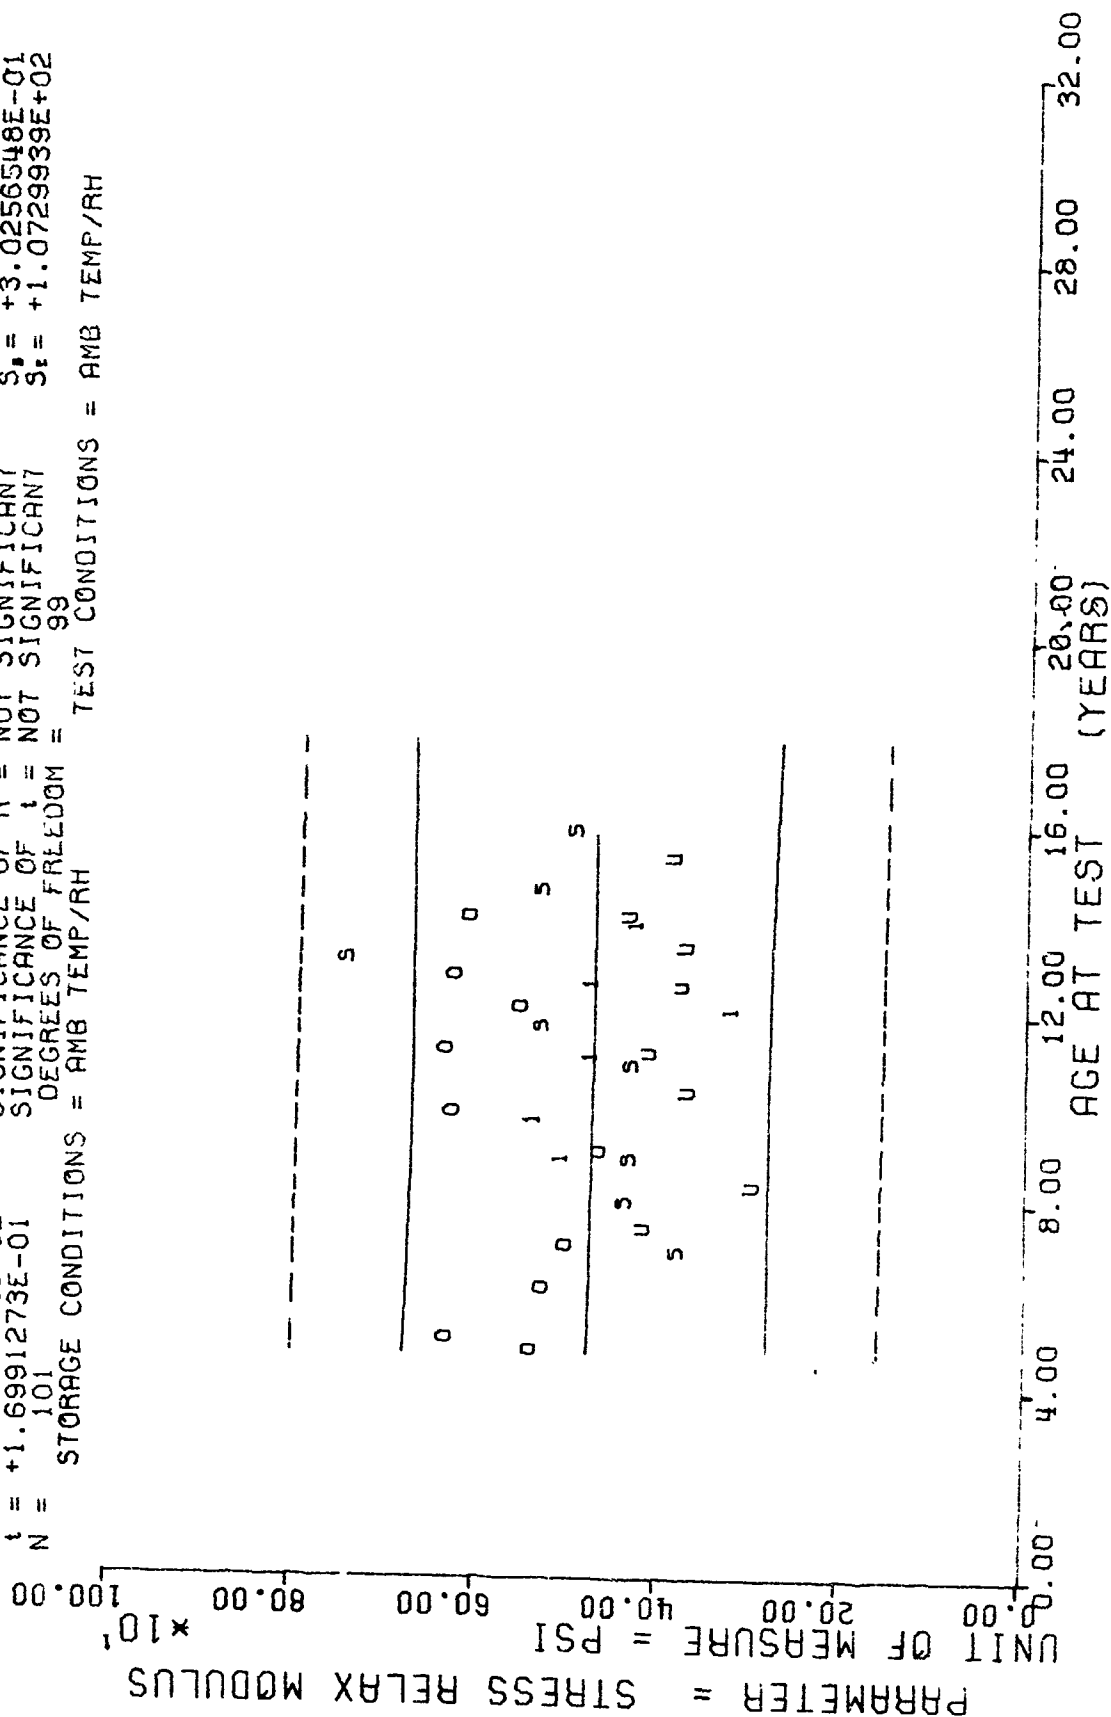

TP-H1011 DISSECTED MTRs, STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 100 SEC

Figure 32

	Y	=	((	+3.8308810E+02	)	+	((	-1.7553639E-02	)	*	X	
F	= +4.1638231E-03			SIGNIFICANCE OF F	=			NOT SIGNIFICANT				G = +8.9658027E+01
R	= -6.5856872E-03			SIGNIFICANCE OF R	=			NOT SIGNIFICANT				S = +2.7203265E-01
t	= +6.4527692E-02			SIGNIFICANCE OF t	=			NOT SIGNIFICANT				S = +9.0121831E+01
N	=			DEGREES OF FREEDOM	=			96				
				STORAGE CONDITIONS = AMB TEMP/RH				TEST CONDITIONS = AMB TEMP/RH				

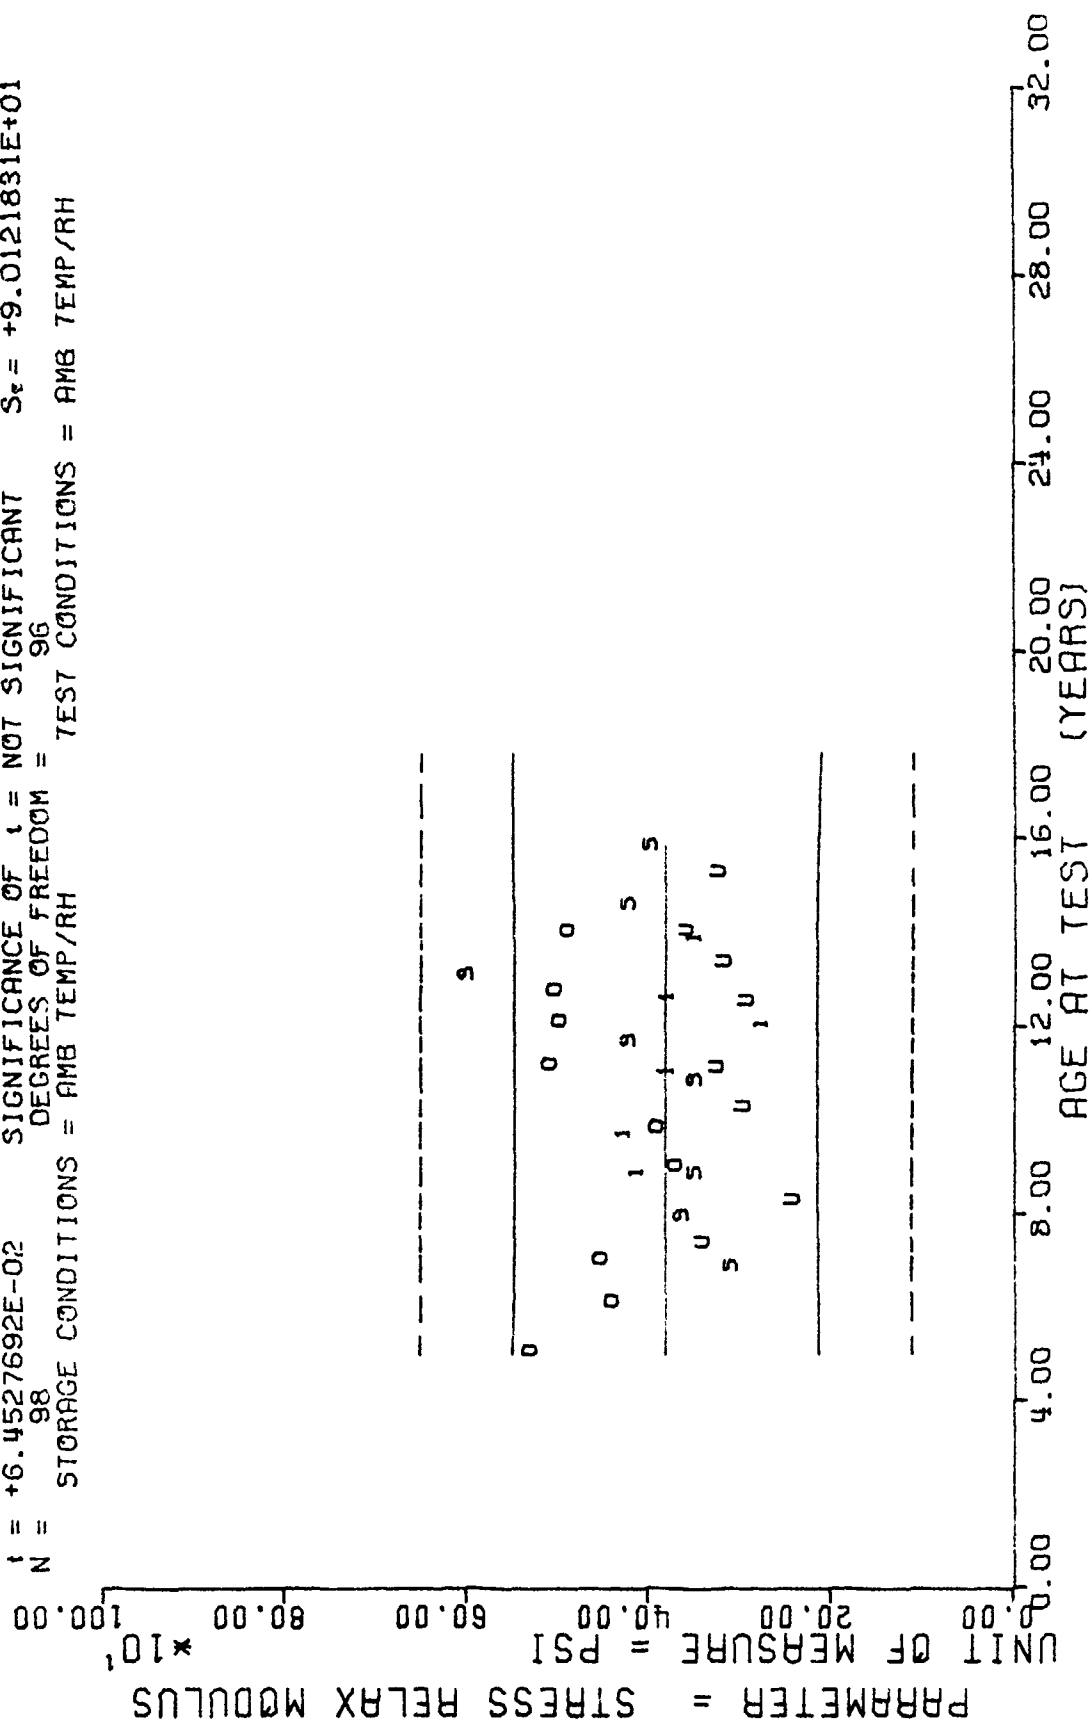


Figure 33


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
57.0	3	166.0	3
60.0	3	168.0	9
73.0	3	175.0	3
82.0	3	183.0	3
84.0	3	190.0	3
88.0	3		
95.0	4		
99.0	3		
106.0	6		
108.0	3		
116.0	3		
118.0	3		
123.0	3		
130.0	3		
132.0	3		
133.0	3		
134.0	3		
140.0	3		
143.0	3		
145.0	3		
150.0	3		
151.0	3		
153.0	3		
157.0	3		
160.0	3		

TP-H1011 DISSECTED MTRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 10 SEC


This sample size summary is applicable to figures 34 thru 37

$Y = ((+6.8508505E+02) + (+2.2592747E-01) * X)$
 $F = +2.9426078E-01$ SIGNIFICANCE OF F = NOT SIGNIFICANT $G_1 = +1.4698727E+02$
 $R = +5.4714459E-02$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +4.1648834E-01$
 $t = +5.4245809E-01$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +1.4751400E+02$
 $N = 100$ DEGREES OF FREEDOM = 98
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

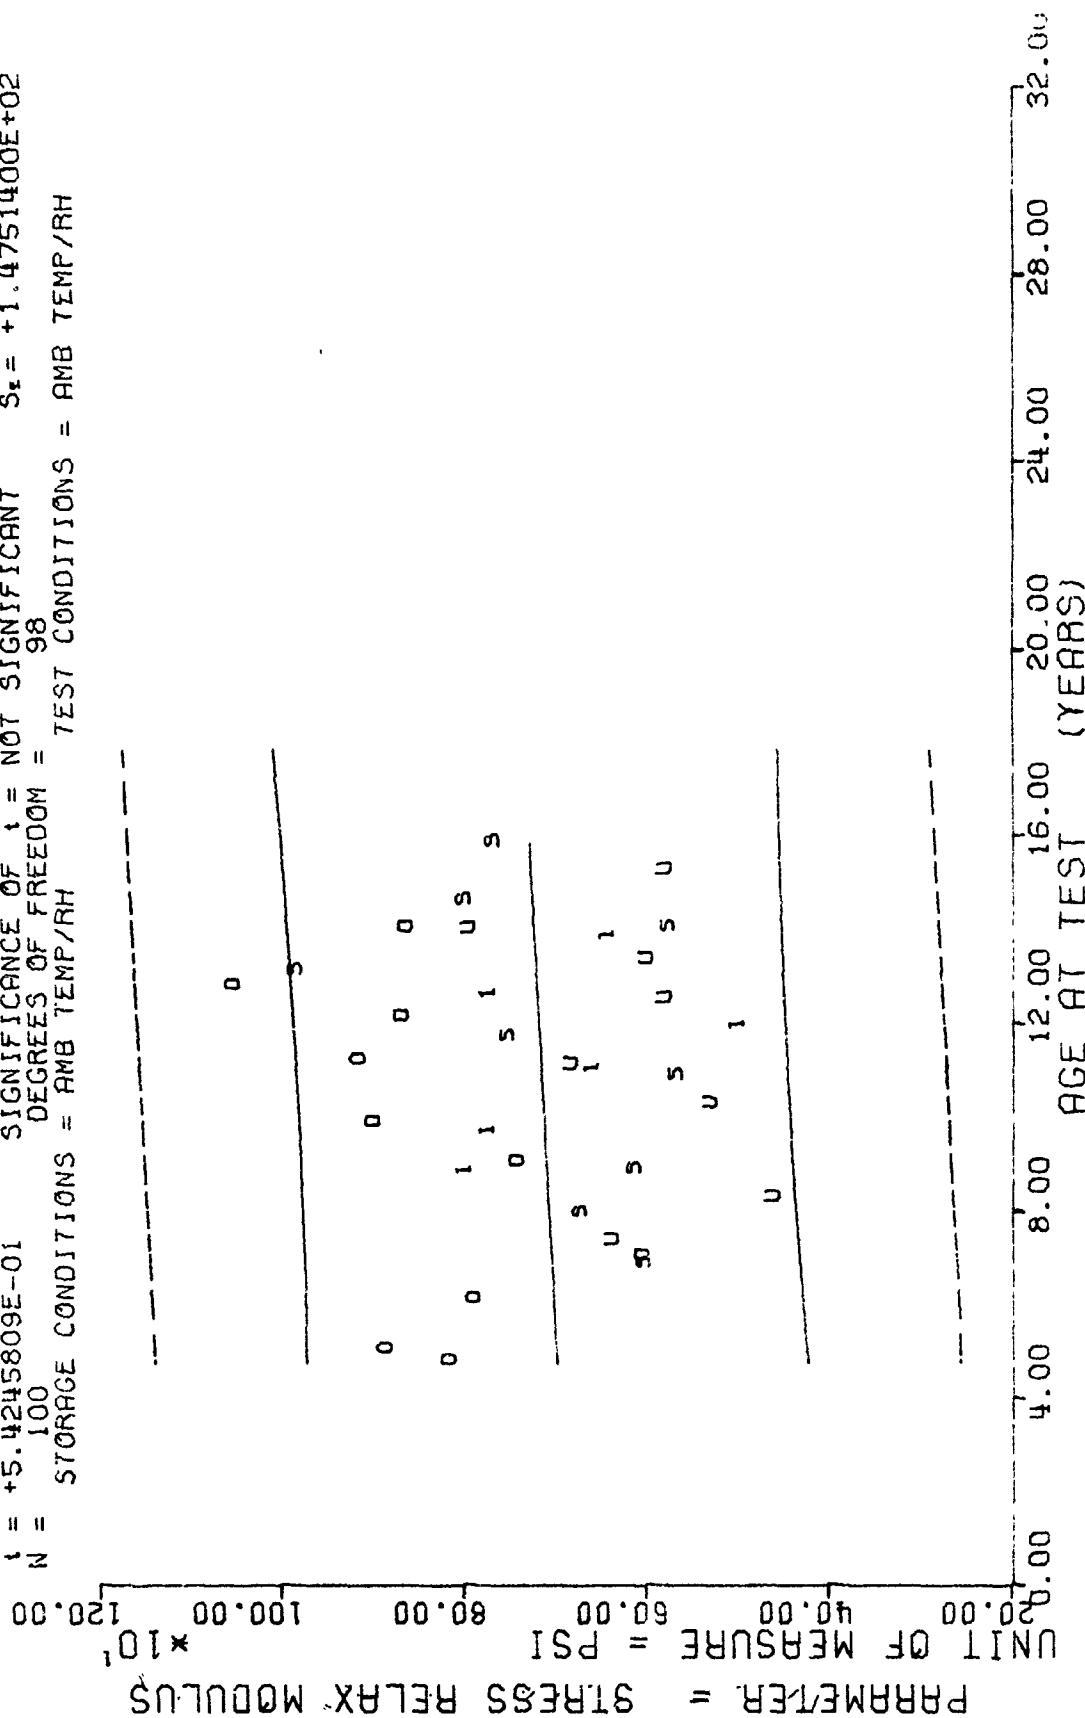


TP-H1011 DISSECTED MTRS. STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 10 SEC

F = +9.5054651E-02
 R = -3.1128853E-02
 t = +3.0830934E-01
 N = 100
 STORAGE CONDITIONS = AMB TEMP/RH
 Y = ((+5.2694983E+02) + (-8.7046370E-02) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 98
 TEST CONDITIONS = AMB TEMP/RH

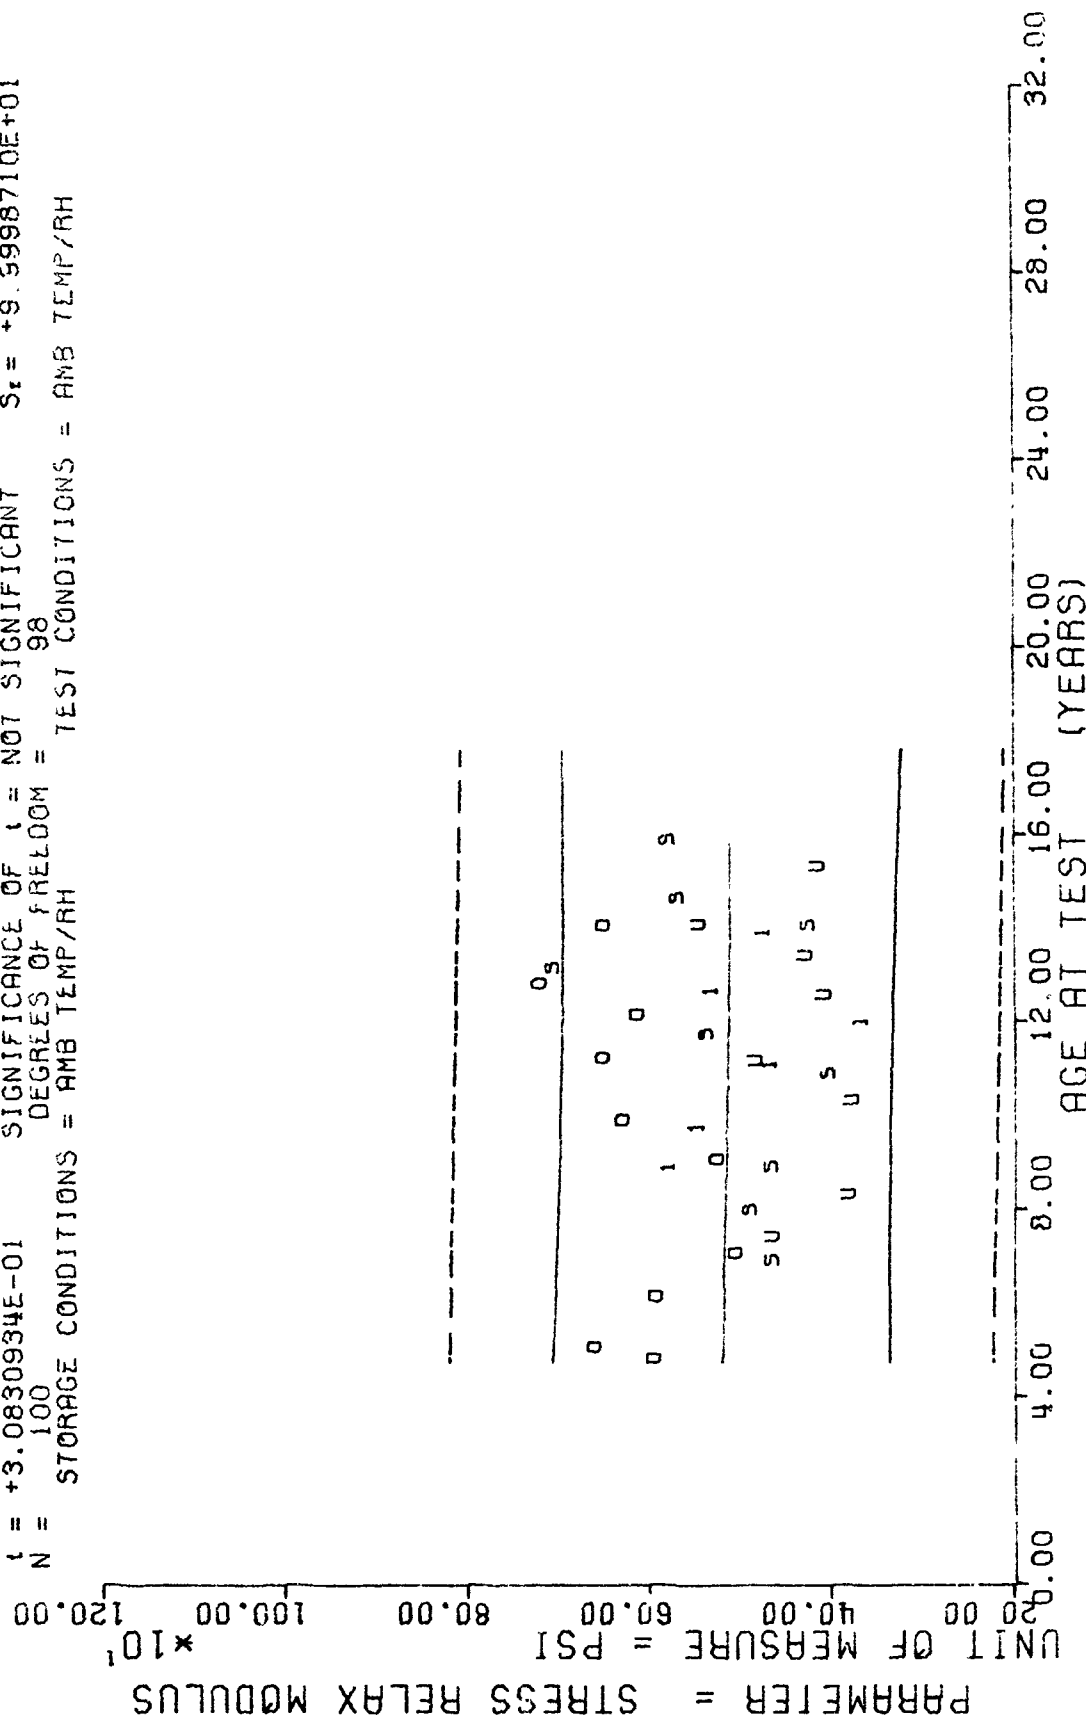

TP-H1011 DISSECTED MTRS. STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 50 SEC


$F = +1.6321510E-01$
 $R = -4.0776109E-02$
 $t = +4.0399888E-01$
 $N = 100$
 $Y = ((+4.9027666E+02) + (-1.0651241E-01) * X)$
 SIGNIFICANCE OF $F =$ NOT SIGNIFICANT $G_1 = +9.2983795E+01$
 SIGNIFICANCE OF $R =$ NOT SIGNIFICANT $S_2 = +2.6364531E-01$
 SIGNIFICANCE OF $t =$ NOT SIGNIFICANT $S_4 = +9.3379271E+01$
 DEGREES OF FREEDOM = 98
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

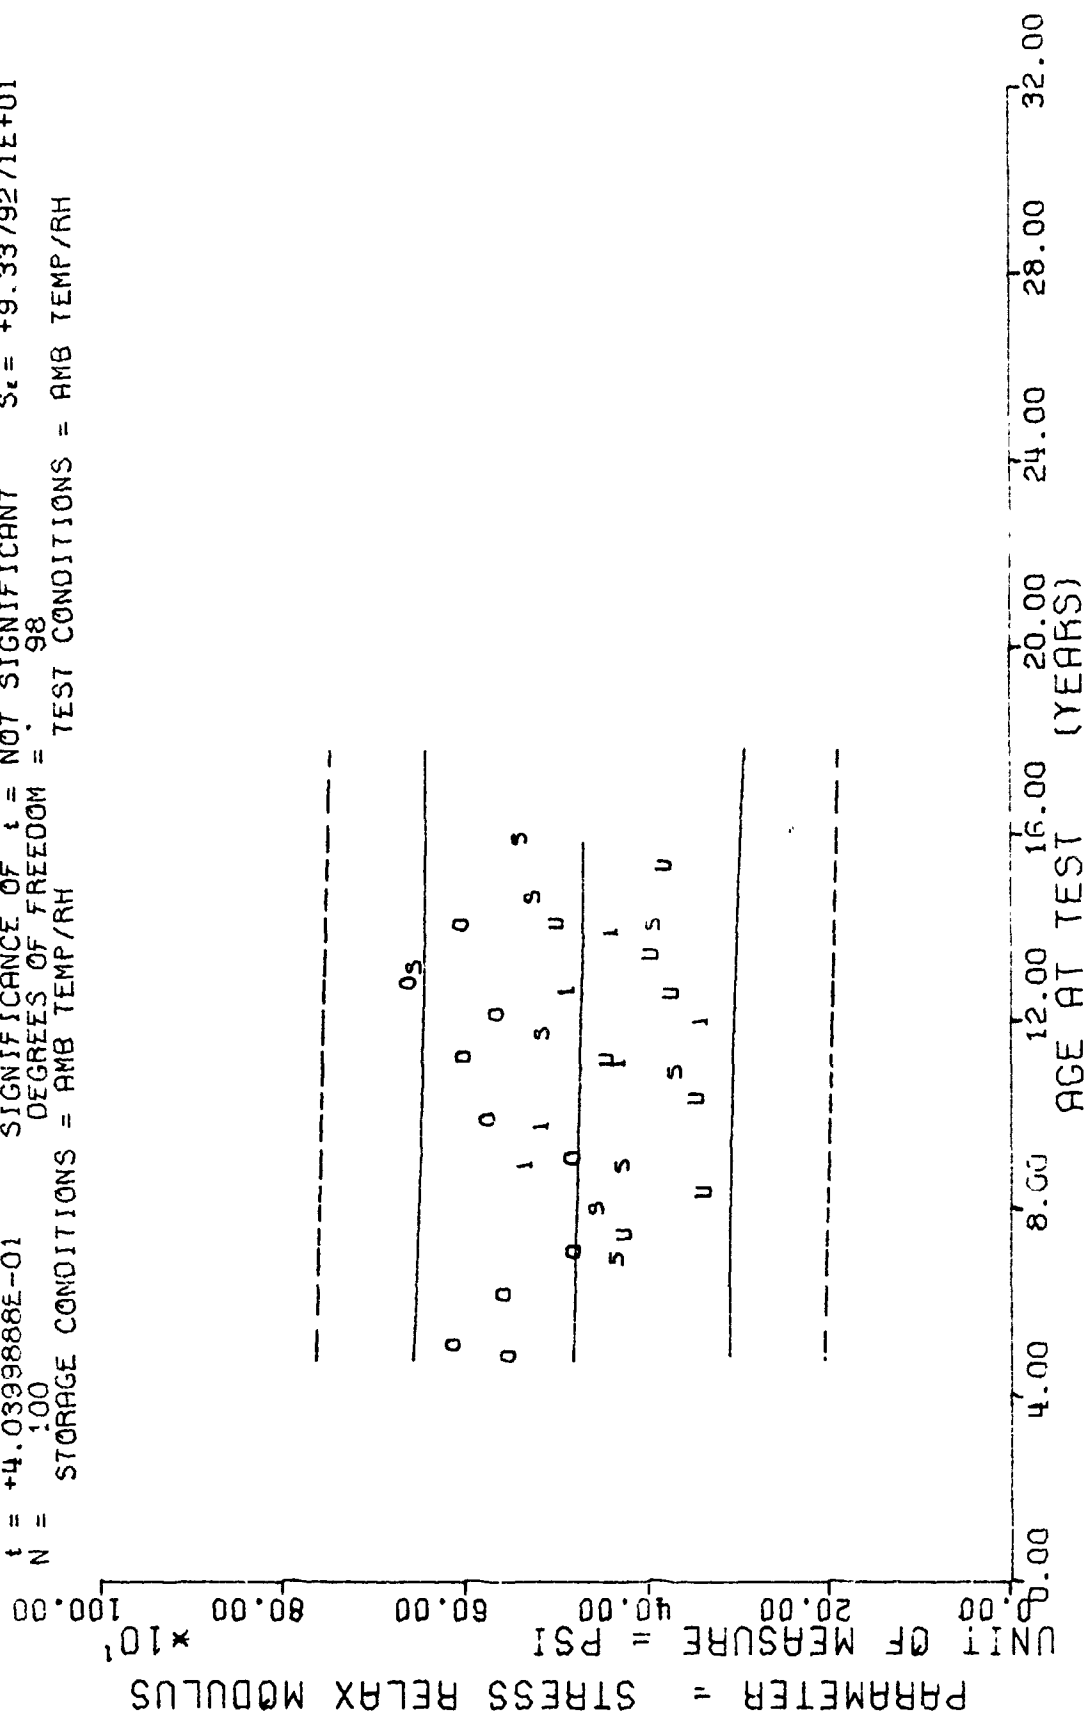

TP-H1011 DISSECTED MTRS. STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 100 SEC

Figure 36

F = +3.6334898E-01
 R = -6.1726439E-02
 t = +6.0278435E-01
 N = 97
 Y = ((+3.9589221E+02) + (-1.3768354E-01) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 95
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

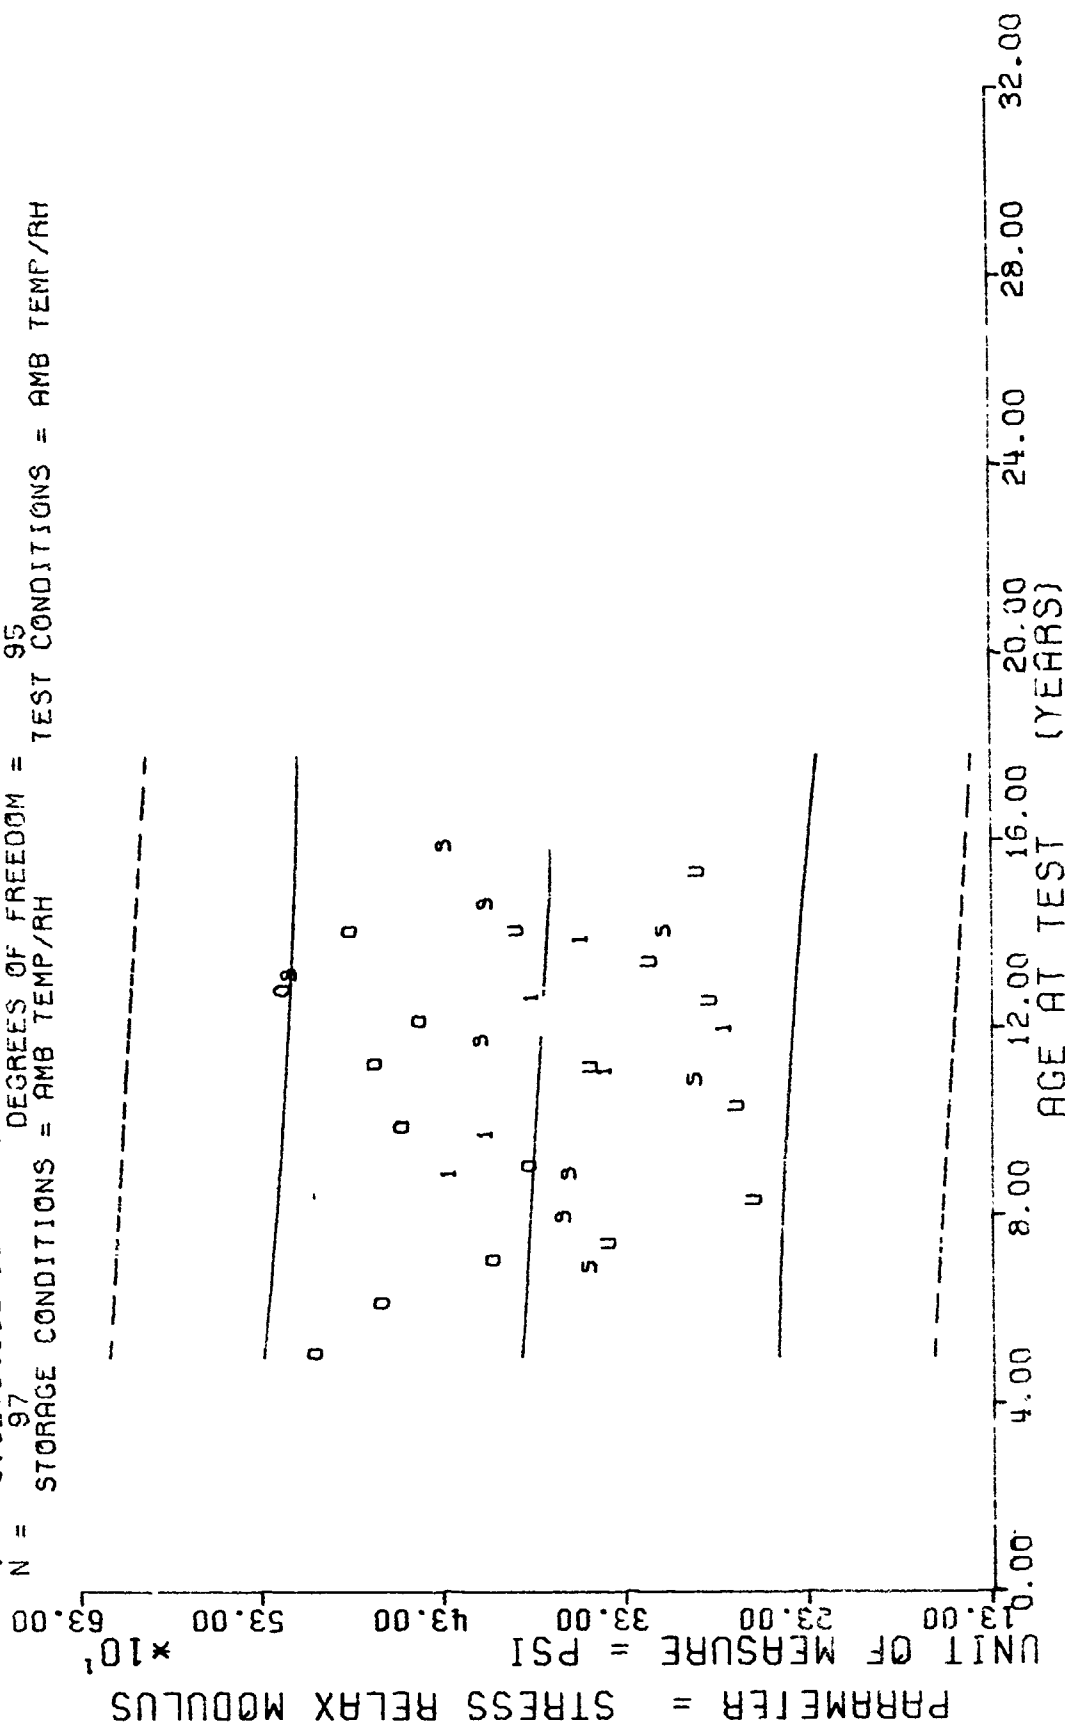

TP-H1011 DISSECTED MTRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 1000 SEC


*** SAMPLE SIZE SUMM KY ***

AGE (MONTHS)	NR SAMPLES
72.0	16
83.0	1
94.0	1
105.0	1
107.0	1
109.0	1
117.0	1
120.0	1
131.0	1
135.0	2
137.0	2
142.0	1
159.0	2

STAGE 1 DSSCOT MRS, CONSTANT STRAIN, STRAIN 0.1 INIT AND 0.01 EVERY 48 HRS

This sample size summary is applicable to figure 38

$Y = ((+3.3048871E+01) + (-1.2955493E-01) * X)$
 $F = +5.2947397E+01$ SIGNIFICANCE OF F = SIGNIFICANT $\sigma_y = +4.9583209E+00$
 $R = -8.0381244E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_e = +1.7804576E-02$
 $t = +7.2764962E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_r = +3.0000443E+00$
 $N = 31$ DEGREES OF FREEDOM = 29
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

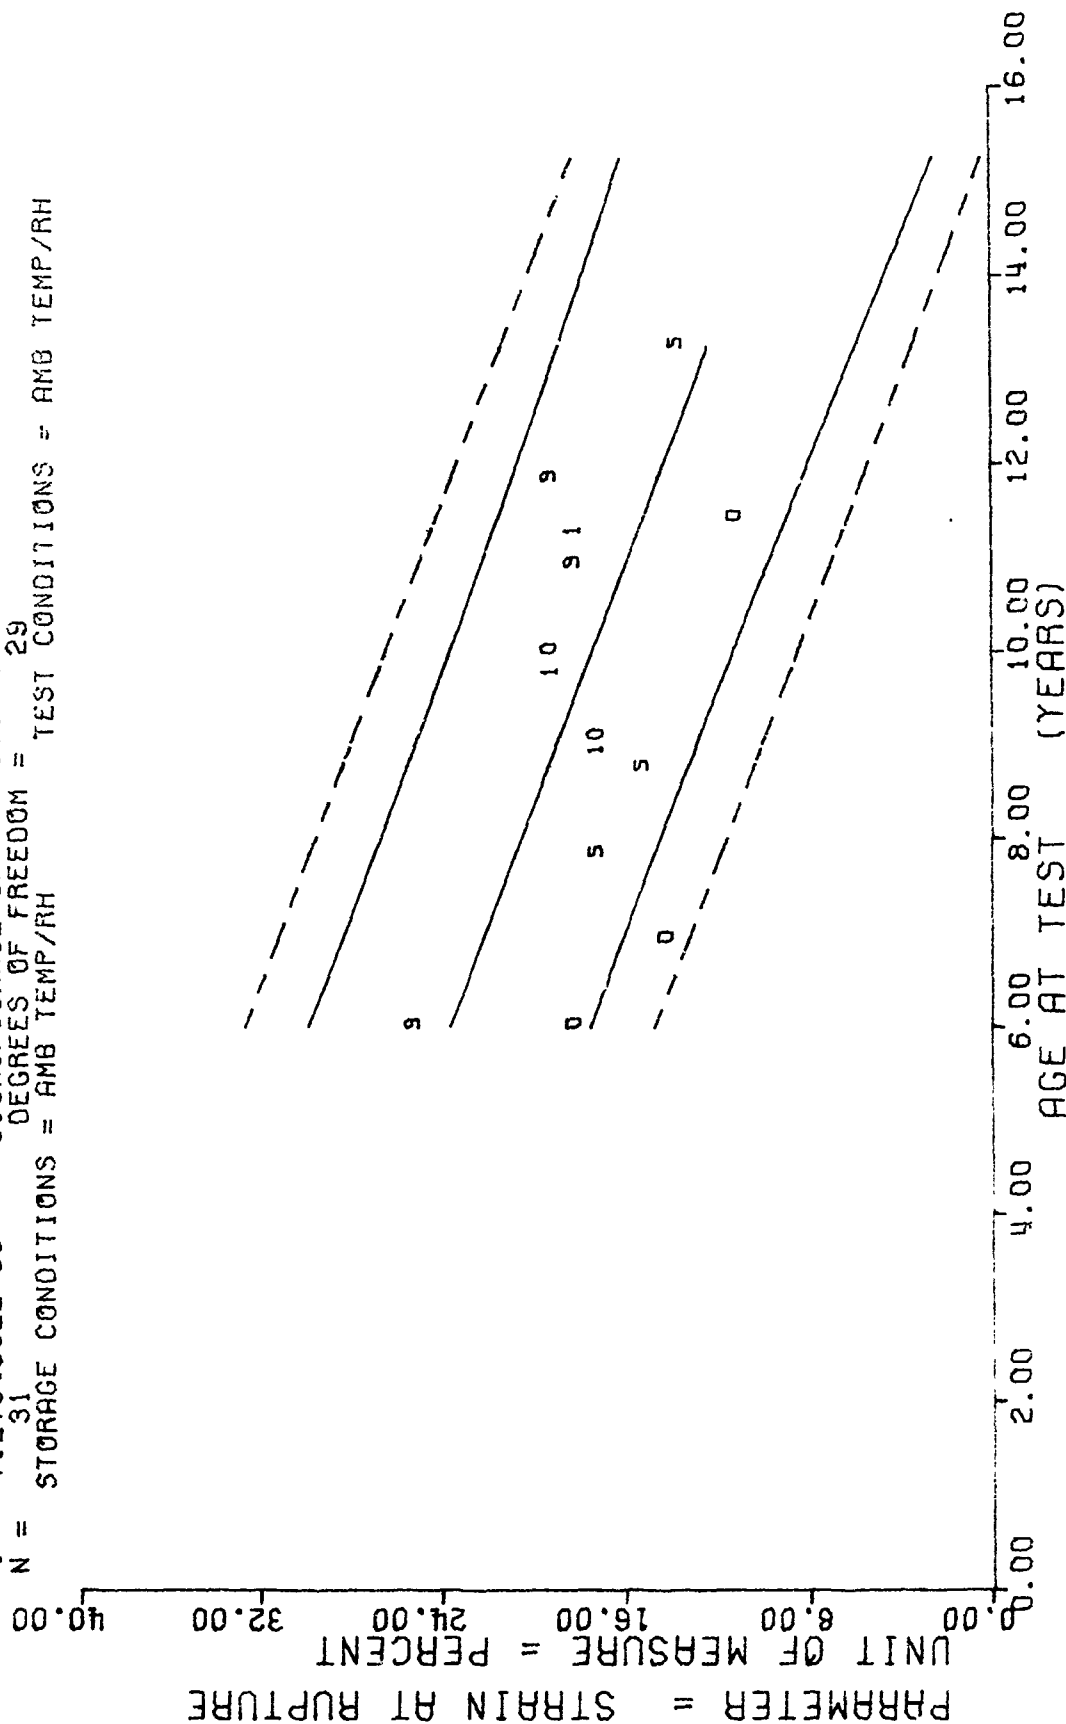

STAGE 1 OSSCTO MTRS. CONSTANT STRAIN, STRAIN 0.1 INIT AND 0.01 EVERY 48 HRS

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
71.0	6	183.0	10
82.0	5	189.0	10
86.0	6		
93.0	1		
97.0	5		
104.0	5		
105.0	5		
107.0	5		
115.0	5		
117.0	5		
122.0	5		
130.0	5		
132.0	10		
134.0	5		
140.0	5		
143.0	3		
145.0	3		
149.0	5		
150.0	5		
152.0	5		
156.0	5		
160.0	3		
167.0	3		
168.0	20		
175.0	5		

STAGE 1 DISSECTED MTRS, SHORE A HARDNESS, 10 SECOND

This sample size summary is applicable to figure 39

$Y = ((+6.6131346E+01) + (-4.6416392E-04) * X)$
 $F = +2.2961006E-03$ SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_1 = +3.9974197E+00$
 $R = -3.8738828E-03$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_0 = +9.6667017E-03$
 $t = +4.7917644E-02$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_e = +4.0104318E+00$
 $N = 155$ DEGREES OF FREEDOM = 153
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

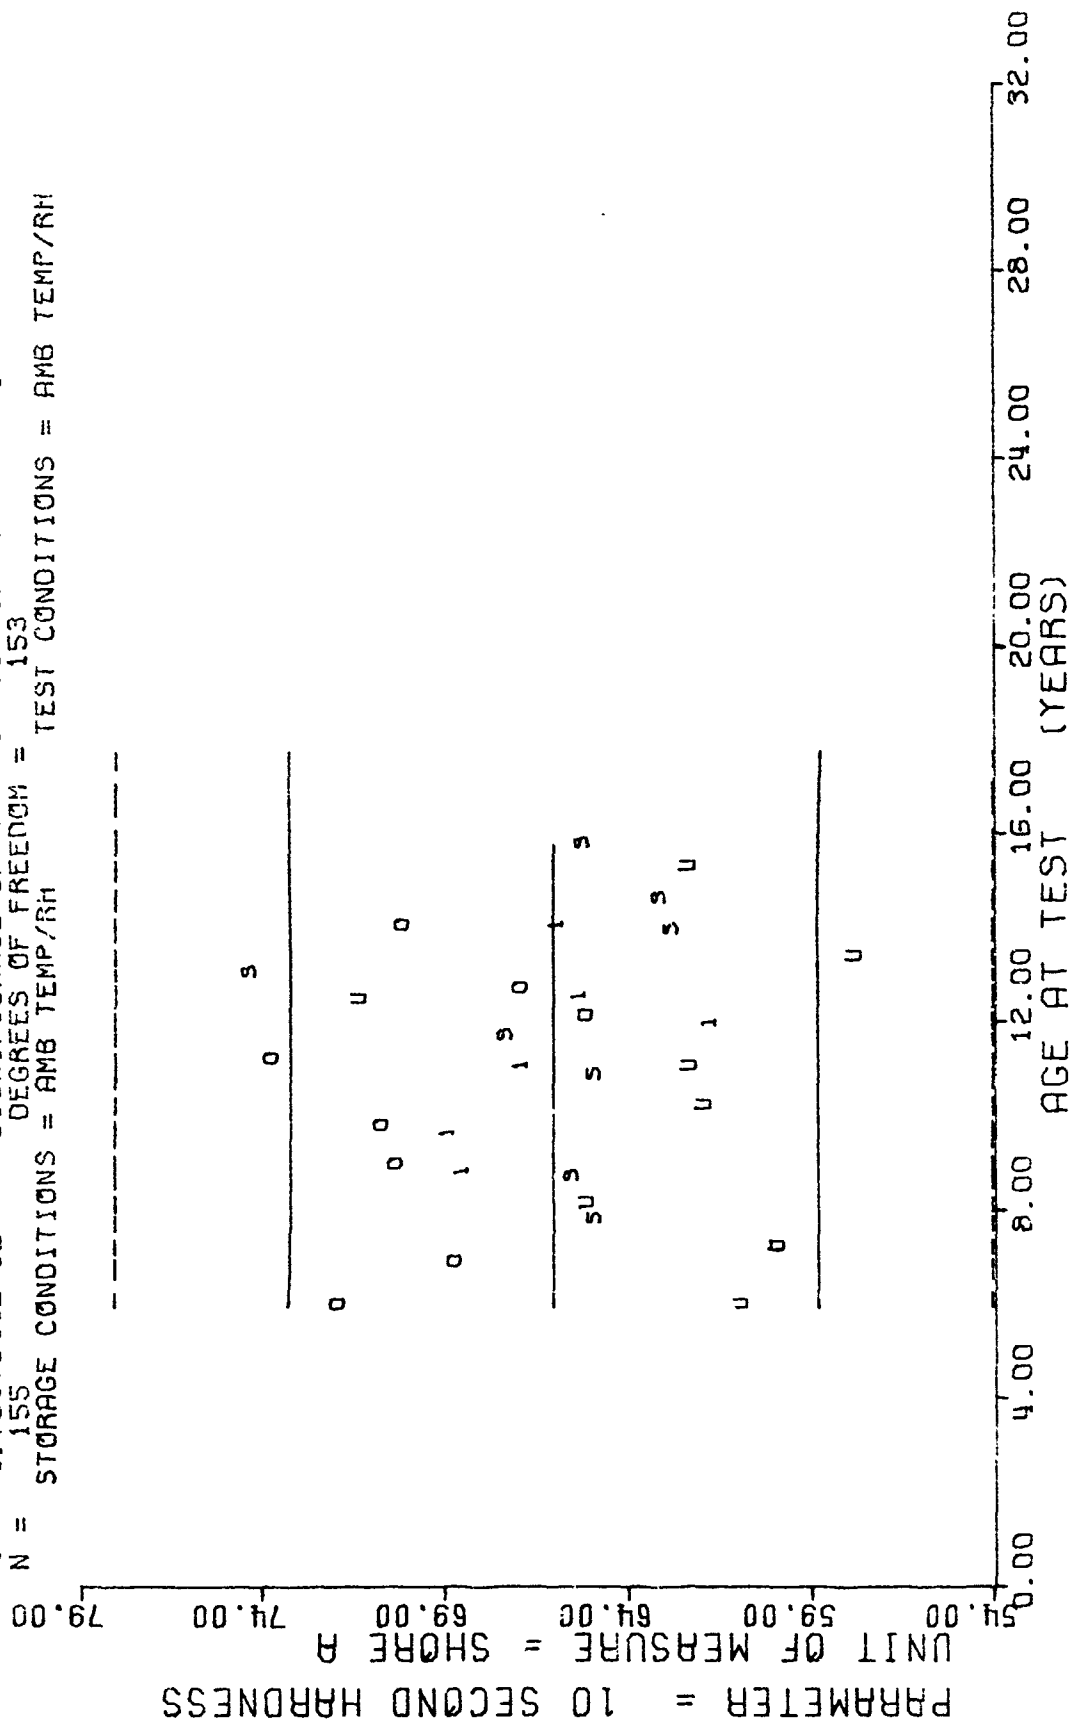


Figure 39


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
74.0	18
83.0	6
89.0	5
97.0	6
98.0	6
105.0	6
106.0	5
108.0	5
118.0	5
120.0	5
123.0	5
135.0	5
142.0	5
152.0	6
154.0	6
168.0	6
169.0	6
170.0	6
176.0	6
185.0	6
193.0	6

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 500 PSI INITIAL PRESSURE

This sample size summary is applicable to figure 40

$Y = \{ (+2.9588253E-01) + (-2.9704153E-04) \times X$
 $F = +7.1074587E+01$ SIGNIFICANCE OF F = SIGNIFICANT $G_1 = +1.9102477E-02$
 $R = -5.9602051E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +3.5233842E-05$
 $t = +8.4305745E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_2 = +1.5398038E-02$
 $N = 131$ DEGREES OF FREEDOM = 129
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

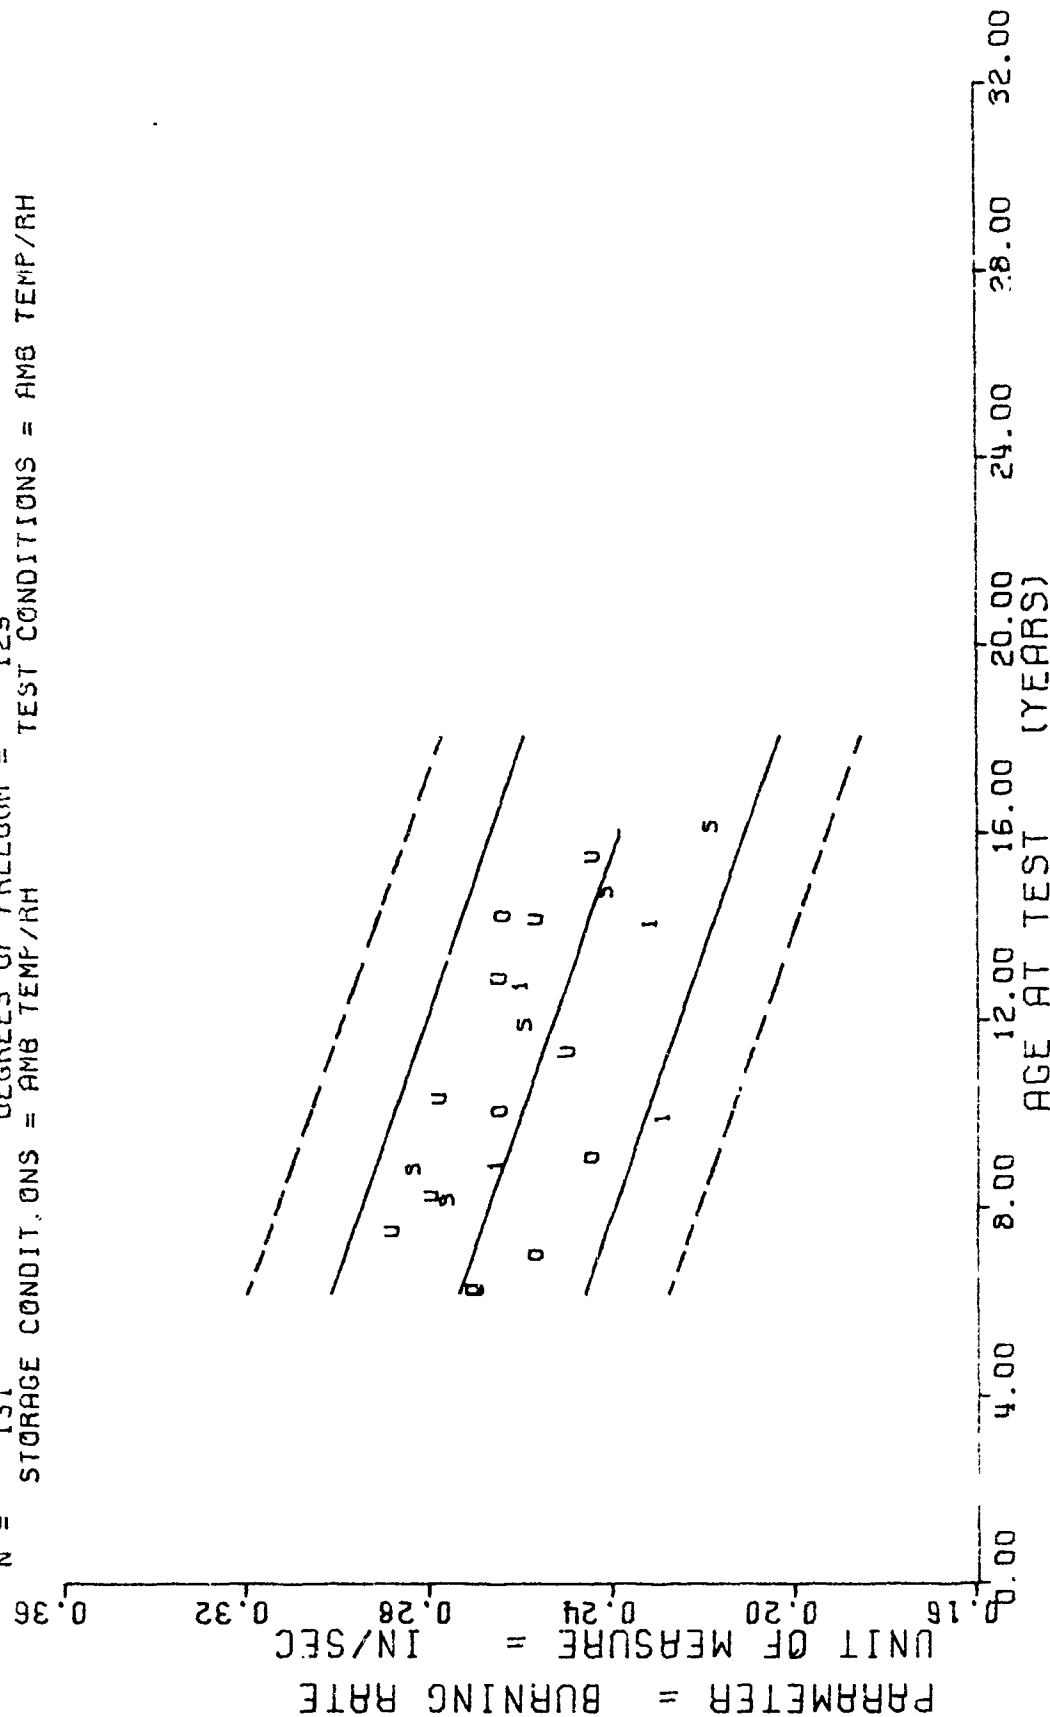

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 500 PSI INITIAL PRESSURE


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
74.0	6	176.0	6
83.0	6	185.0	6
89.0	6	193.0	6
97.0	6		
98.0	6		
105.0	6		
106.0	5		
108.0	5		
118.0	5		
120.0	5		
123.0	5		
130.0	10		
135.0	5		
137.0	8		
139.0	5		
142.0	5		
145.0	6		
147.0	5		
152.0	5		
154.0	11		
161.0	5		
162.0	5		
168.0	6		
169.0	11		
170.0	6		

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 1000 PSI INITIAL PRESSURE

This sample size summary is applicable to figure 41

$F = +1.4356181E+02$
 $R = -6.7664034E-01$
 $\{ = +1.1981728E+01$
 $N = 172$
 $Y = \{ (+3.6862352E-01) + (-4.3013127E-04) \times X_4$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF $\{$ = SIGNIFICANT
 DEGREES OF FREEDOM = 170
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

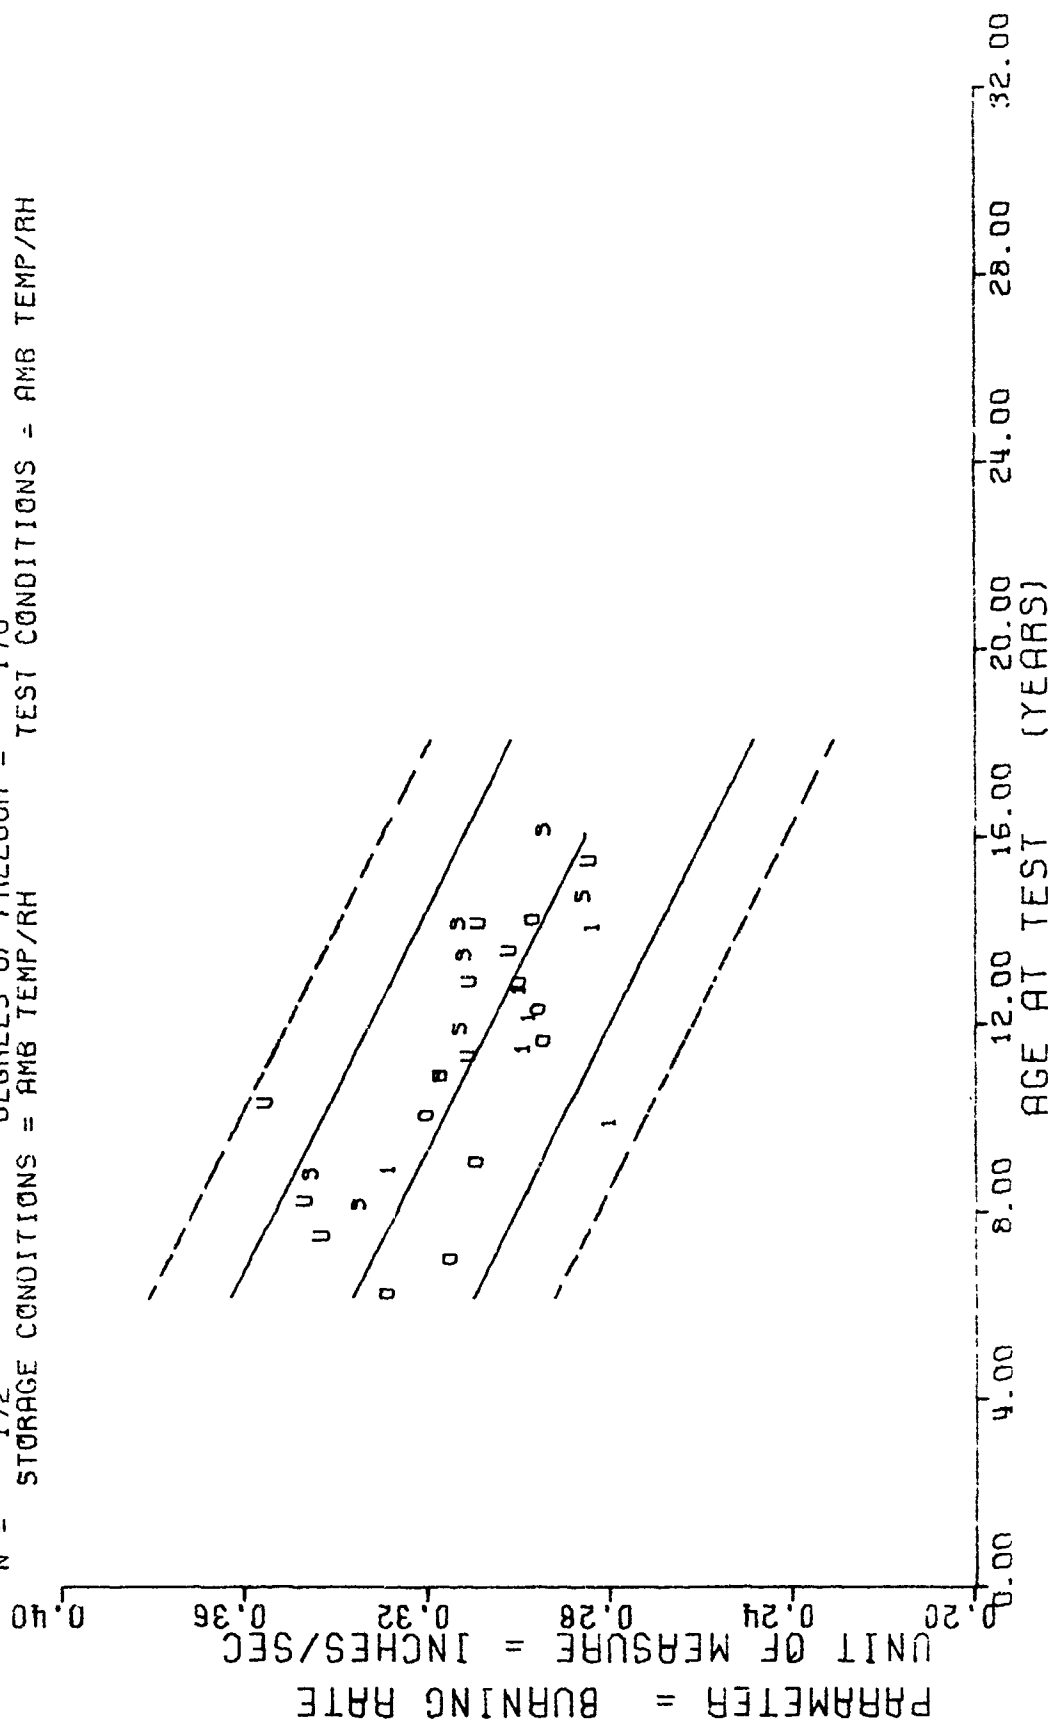

STAGE 1 DISSECTIONED MOTORS, BURNING RATE AT 1000 PSI INITIAL PRESSURE


*** SAMPLE SIZE SUMMARY **

AGE (MONTHS)	NR SAMPLES
74.0	3
76.0	3
83.0	3
91.0	3
98.0	6
105.0	3
108.0	1
110.0	1
125.0	1
132.0	1
136.0	3
138.0	3
152.0	3
153.0	3
154.0	3
160.0	3
167.0	3
169.0	6
176.0	3
184.0	3
191.0	3

STAGE 1 DISSECTED MOTORS, HEAT OF EXPLOSION

This sample size summary is applicable to figure 42

$Y = ((+1.5414750E+03) + (+4.4604610E-02) \times X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_1 = +9.2163720E+00$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_0 = +3.1466436E-02$
 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_1 = +9.1398123E+00$
 DEGREES OF FREEDOM = 59
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

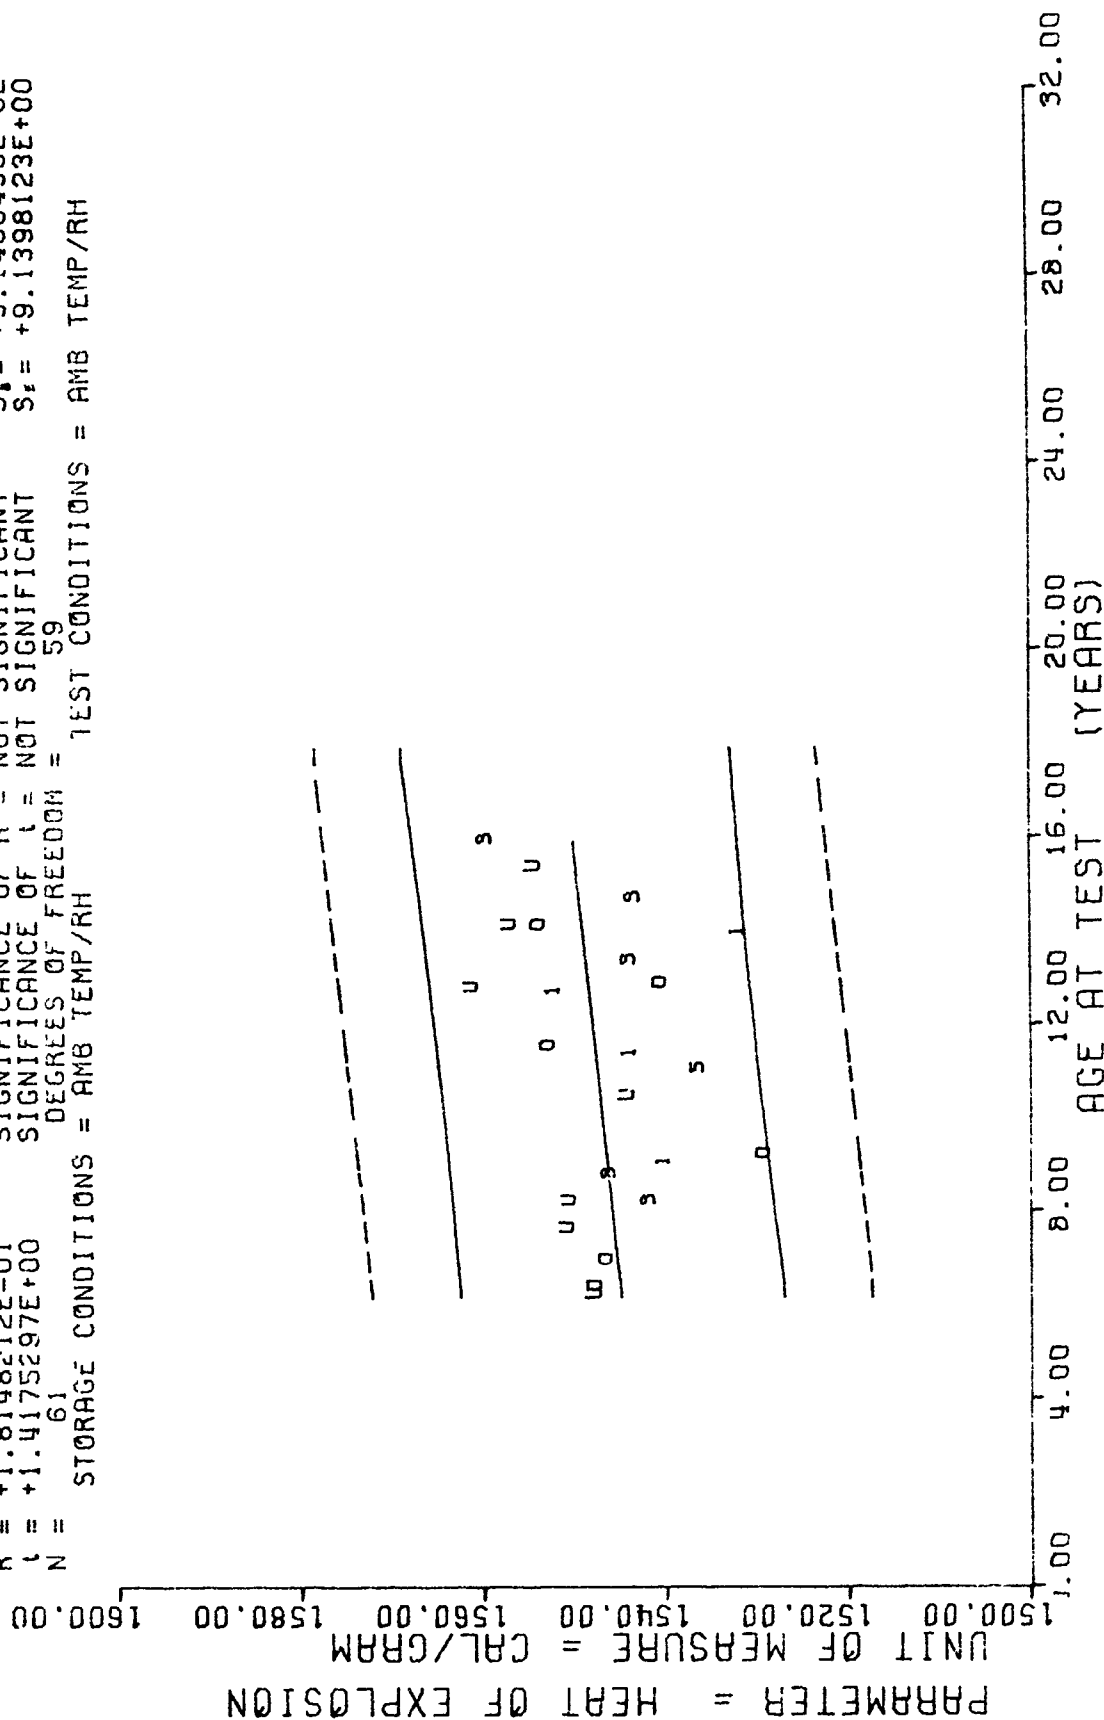

STAGE 1 DISSECTIONED MOTORS, HEAT OF EXPLOSION


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	1
88.0	1
96.0	1
108.0	1
110.0	1
116.0	1
118.0	1
125.0	1
133.0	1
134.0	2
136.0	1
140.0	1
145.0	1
147.0	1
151.0	1
152.0	1
154.0	1
158.0	1
162.0	1
159.0	2
176.0	1

STAGE I DISSECTED MTRS, IGNITABILITY, IGNIN THRSHLD POINT 168 (CAL/SQCM)/SEC

This sample size summary is applicable to figure 43

$Y = ((+5.7692488E+01) + (-3.8549585E-03) * X)$
 $F = +5.6660960E-03$ SIGNIFICANCE OF F = NOT SIGNIFICANT $S_1 = +6.3507492E+00$
 $R = -1.6423803E-02$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_2 = +5.1212708E-02$
 $t = +7.5273474E-02$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_3 = +6.4993223E+00$
 $N = 23$ DEGREES OF FREEDOM = 21
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 168 CAL/SQCM/SEC

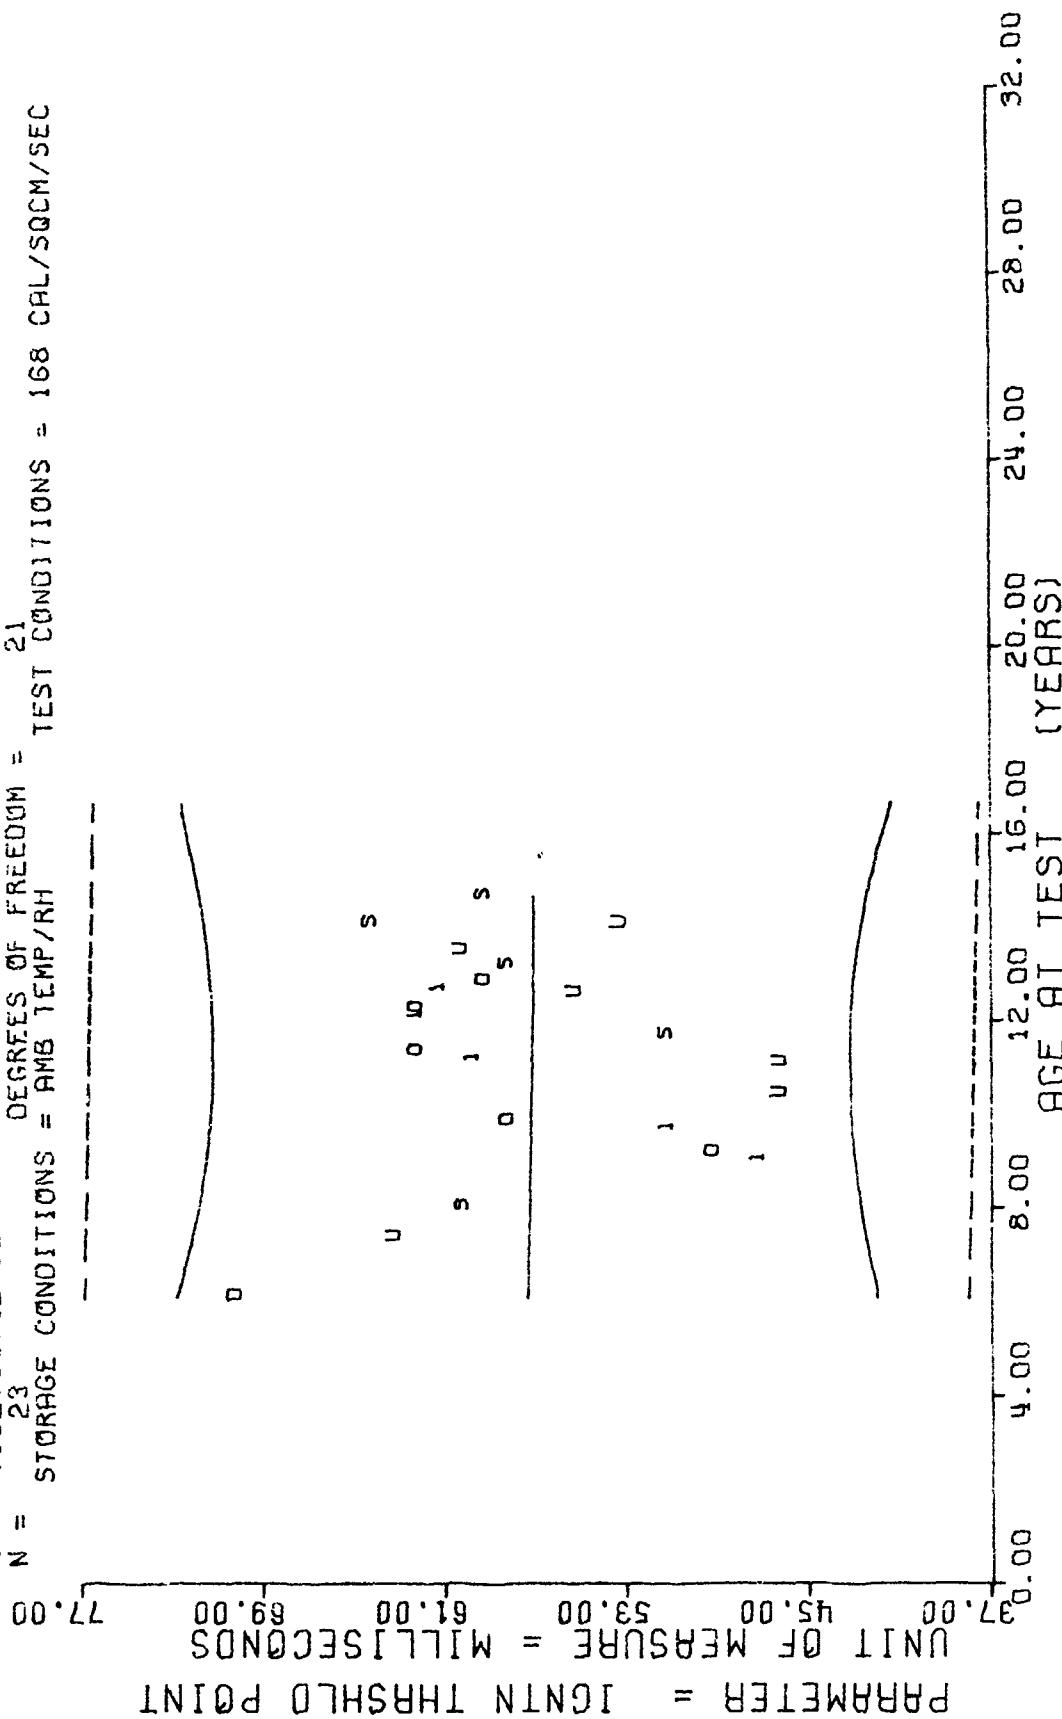

STAGE 1 DISSECTED MTRS. IGNITABILITY. IGNITION THRESHOLD POINT 168 (CAL/SQCM) / SEC


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	4
75.0	3
83.0	2
90.0	3
98.0	9
105.0	5
114.0	3
118.0	3
133.0	3
135.0	3
137.0	3
140.0	3
152.0	2
154.0	3
160.0	3
167.0	3
169.0	9
176.0	3
184.0	5
192.0	3

STAGE 1 DISSECTED MOTORS, DTA, ENDOTHERM 1, 12 DEGREE C RISE/MINUTE


This sample size summary is applicable to figures 44 and 45

$Y = ((+2.4200173E+02) + (+1.8729140E-04) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_1 = +2.1621644E+00$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +6.8734534E-03$
 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +2.1769123E+00$
 N = 75
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

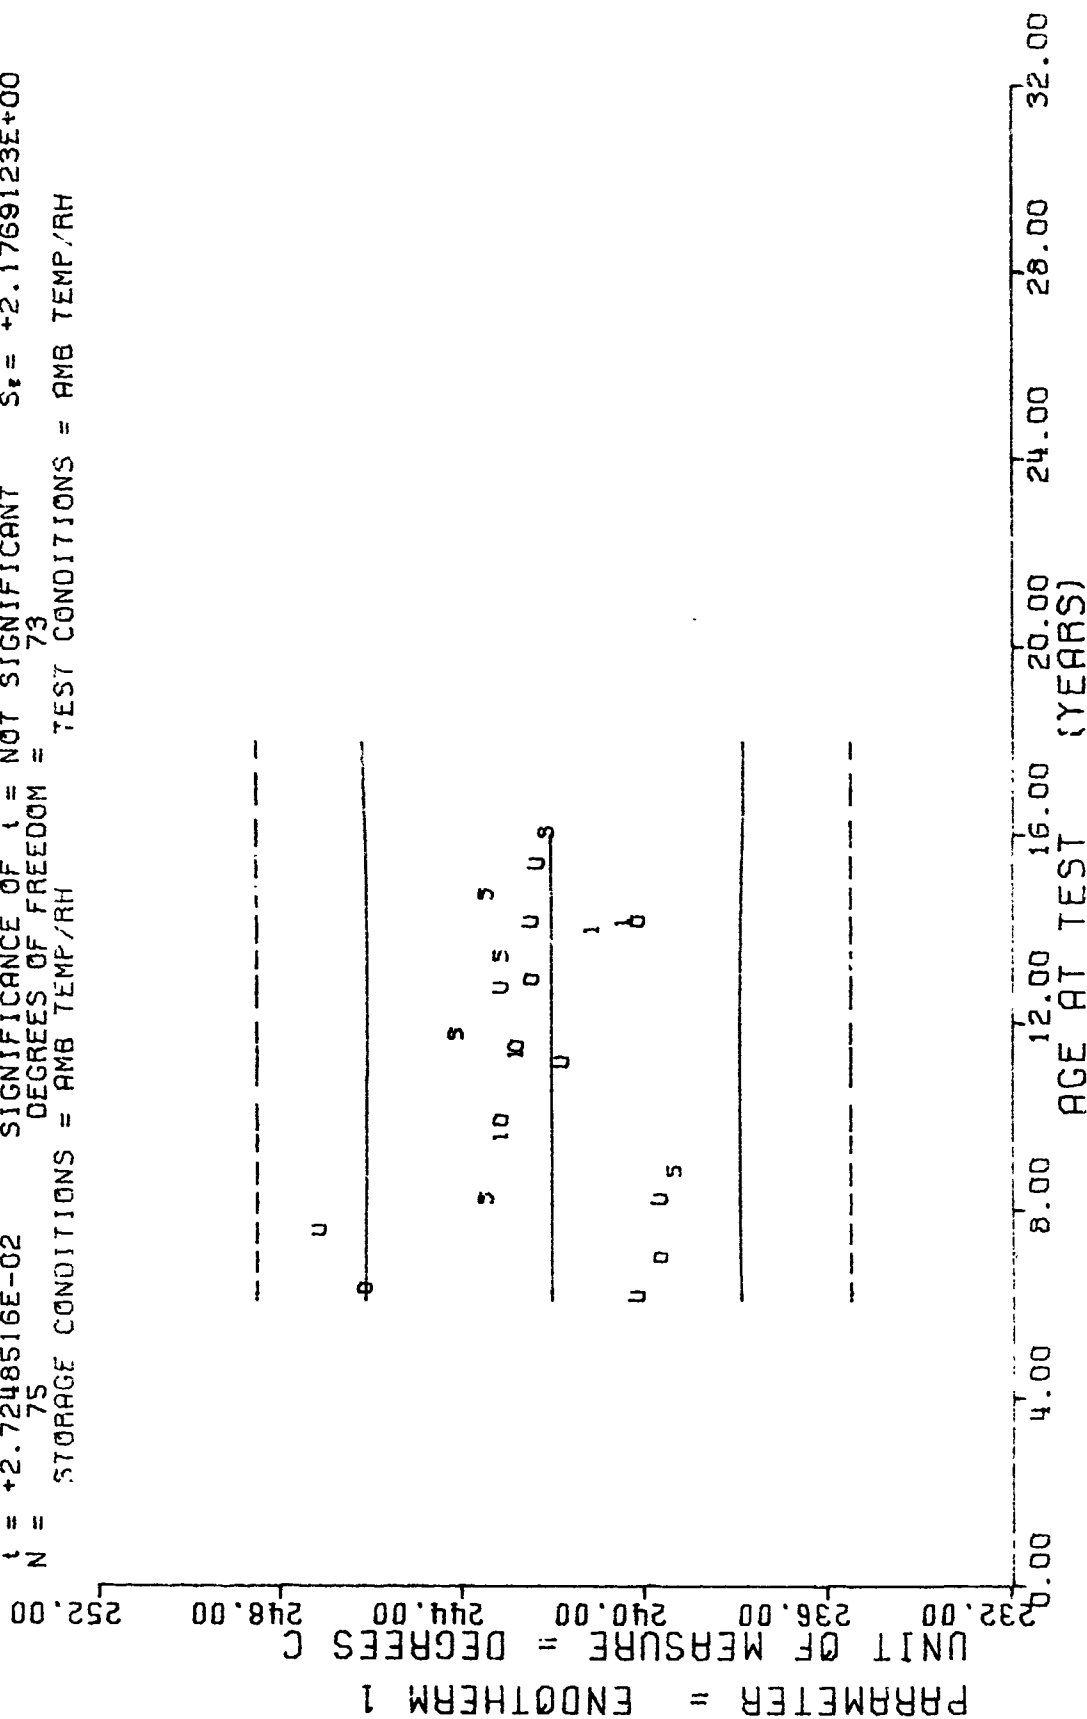

STAGE 1 DISSECTED MOTORS, OTA, ENDOTHERM 1, 12 DEGREE C RISE/MINUTE

$Y = ((+2.9816090E+02) + (-2.2444927E-02) \times X)$
 $F = +1.9230651E+00$ SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_f = +5.1579729E+00$
 $R = -1.6020985E-01$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_e = +1.6185317E-02$
 $t = +1.3867462E+00$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_f = +5.1261008E+00$
 $N = 75$ DEGREES OF FREEDOM = 73
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

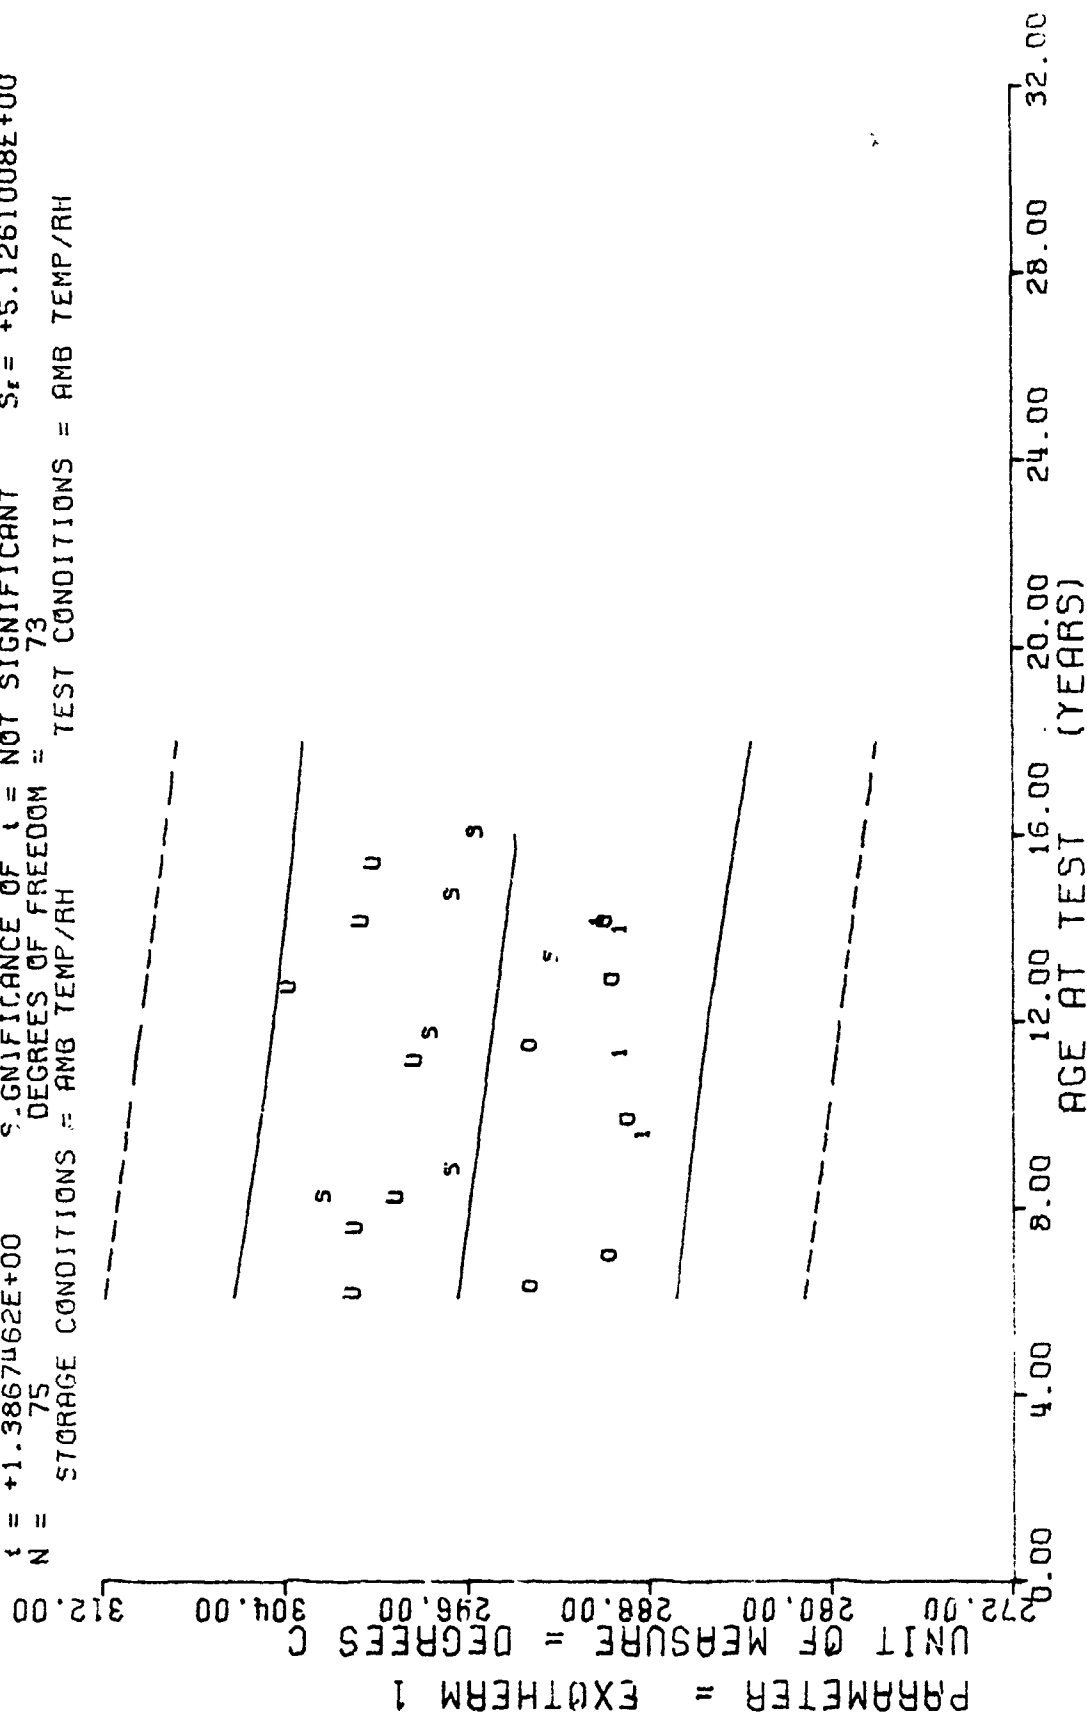

STAGE 1 DISSECTED MOTORS, DTA, EXOTHERM 1, 12 DEGREE C RISE/MINUTE

Figure 45


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	4
75.0	3
83.0	2
90.0	3
98.0	9
105.0	5
114.0	2
133.0	3
135.0	2
140.0	3
152.0	2
154.0	1
167.0	2
169.0	6
176.0	2
184.0	5
192.0	3

STAGE 1 DISSECTED MOTORS, DTA IGNITION TEMP, 12 DEG C RISE/MINUTE

This sample size summary is applicable to figure 46

$Y = ((+3.5297303E+02) + (+1.0115087E-01) * X)$
 $F = +1.5056746E+01$ SIGNIFICANCE OF F = SIGNIFICANT $S_x = +8.6571424E+00$
 $R = +4.6359696E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_y = +2.6067782E-02$
 $t = +3.8803023E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_z = +7.7400469E+00$
 $N = 57$ DEGREES OF FREEDOM = 55
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

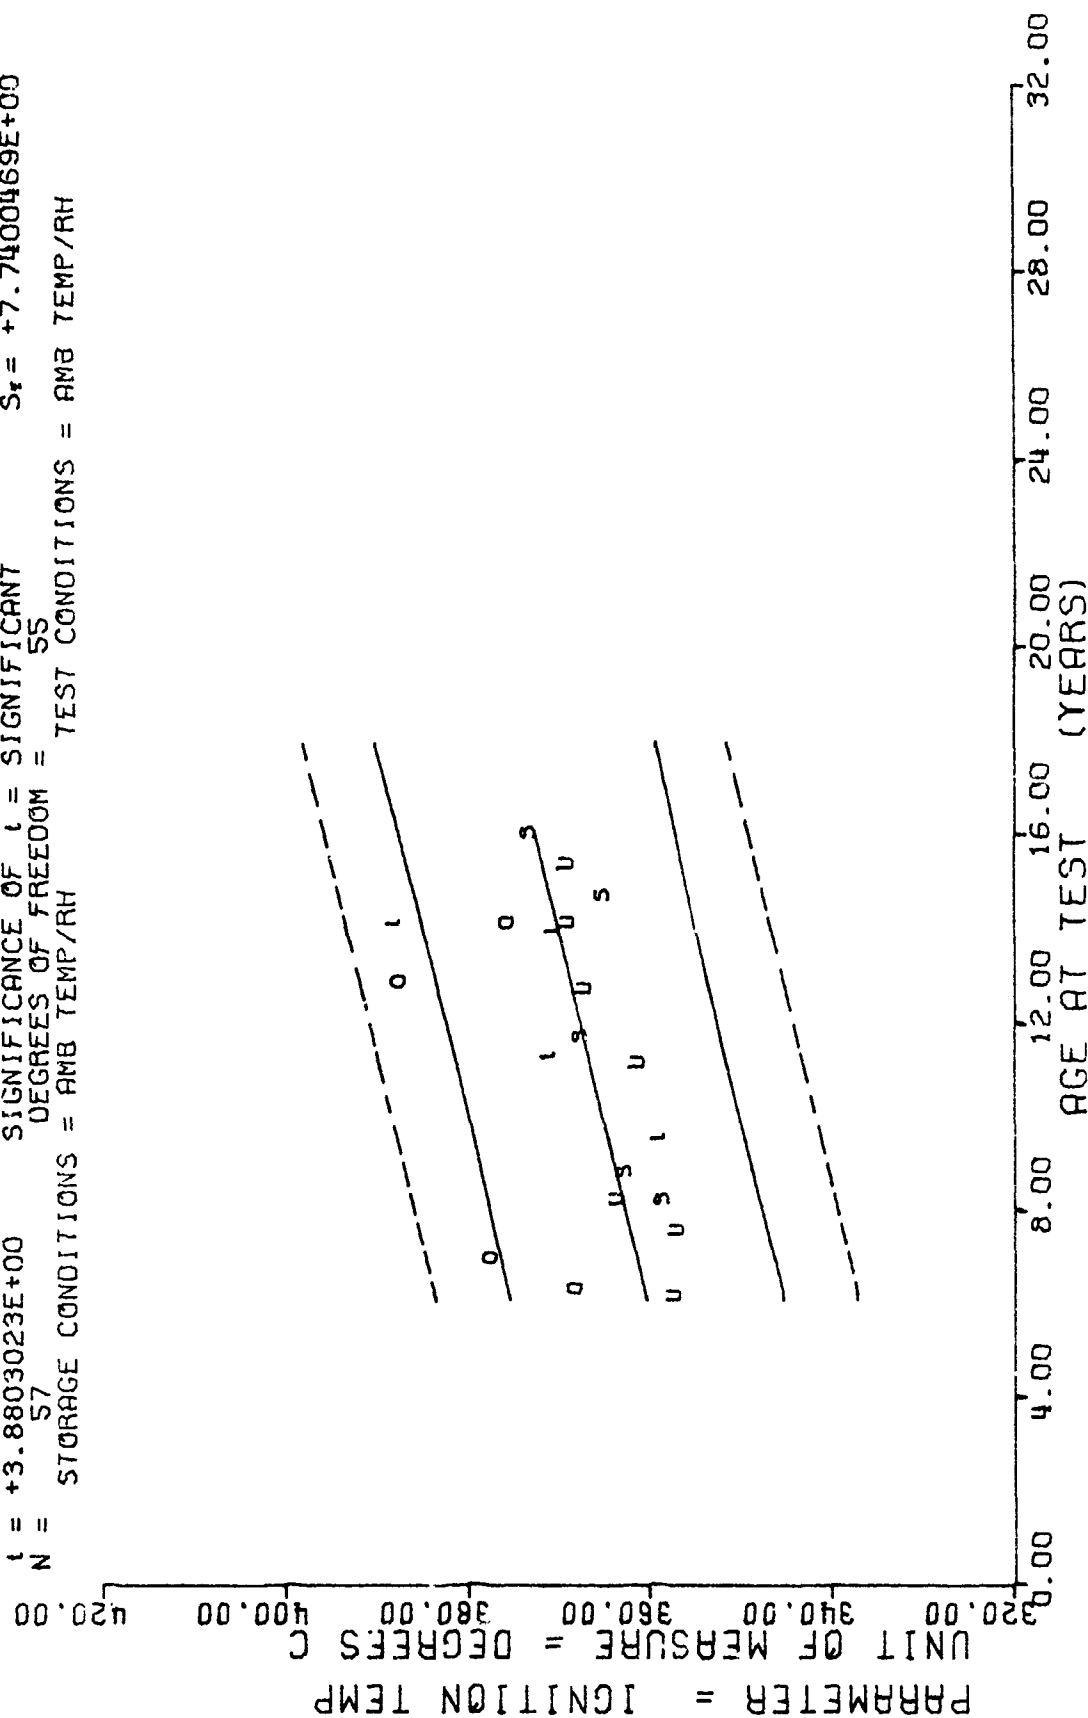

STAGE 1 DISSECTED MOTORS, DTA IGNITION TEMP, 12 DEG C RISE/MINUTE

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
133.0	4
135.0	4
146.0	4
148.0	4
150.0	4
152.0	4
154.0	4
157.0	4
163.0	4
167.0	6
169.0	4
170.0	4
176.0	4
184.0	6
191.0	6

DISSECTED MTR, STAGE 1, TP-H1011, SOL GEL, PERCENT EXTRACTABLES

This sample size summary is applicable to figures 47 thru 50

$Y = (1 + 8.0798083E+00) + (-6.2924187E-03) * X$
 $F = +4.9398380E+00$ SIGNIFICANCE OF F = SIGNIFICANT $G_4 = +3.9922579E-01$
 $R = -2.6768326E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_2 = +2.8311394E-03$
 $t = +2.2225746E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_1 = +3.8765031E-01$
 $N = 66$ DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH


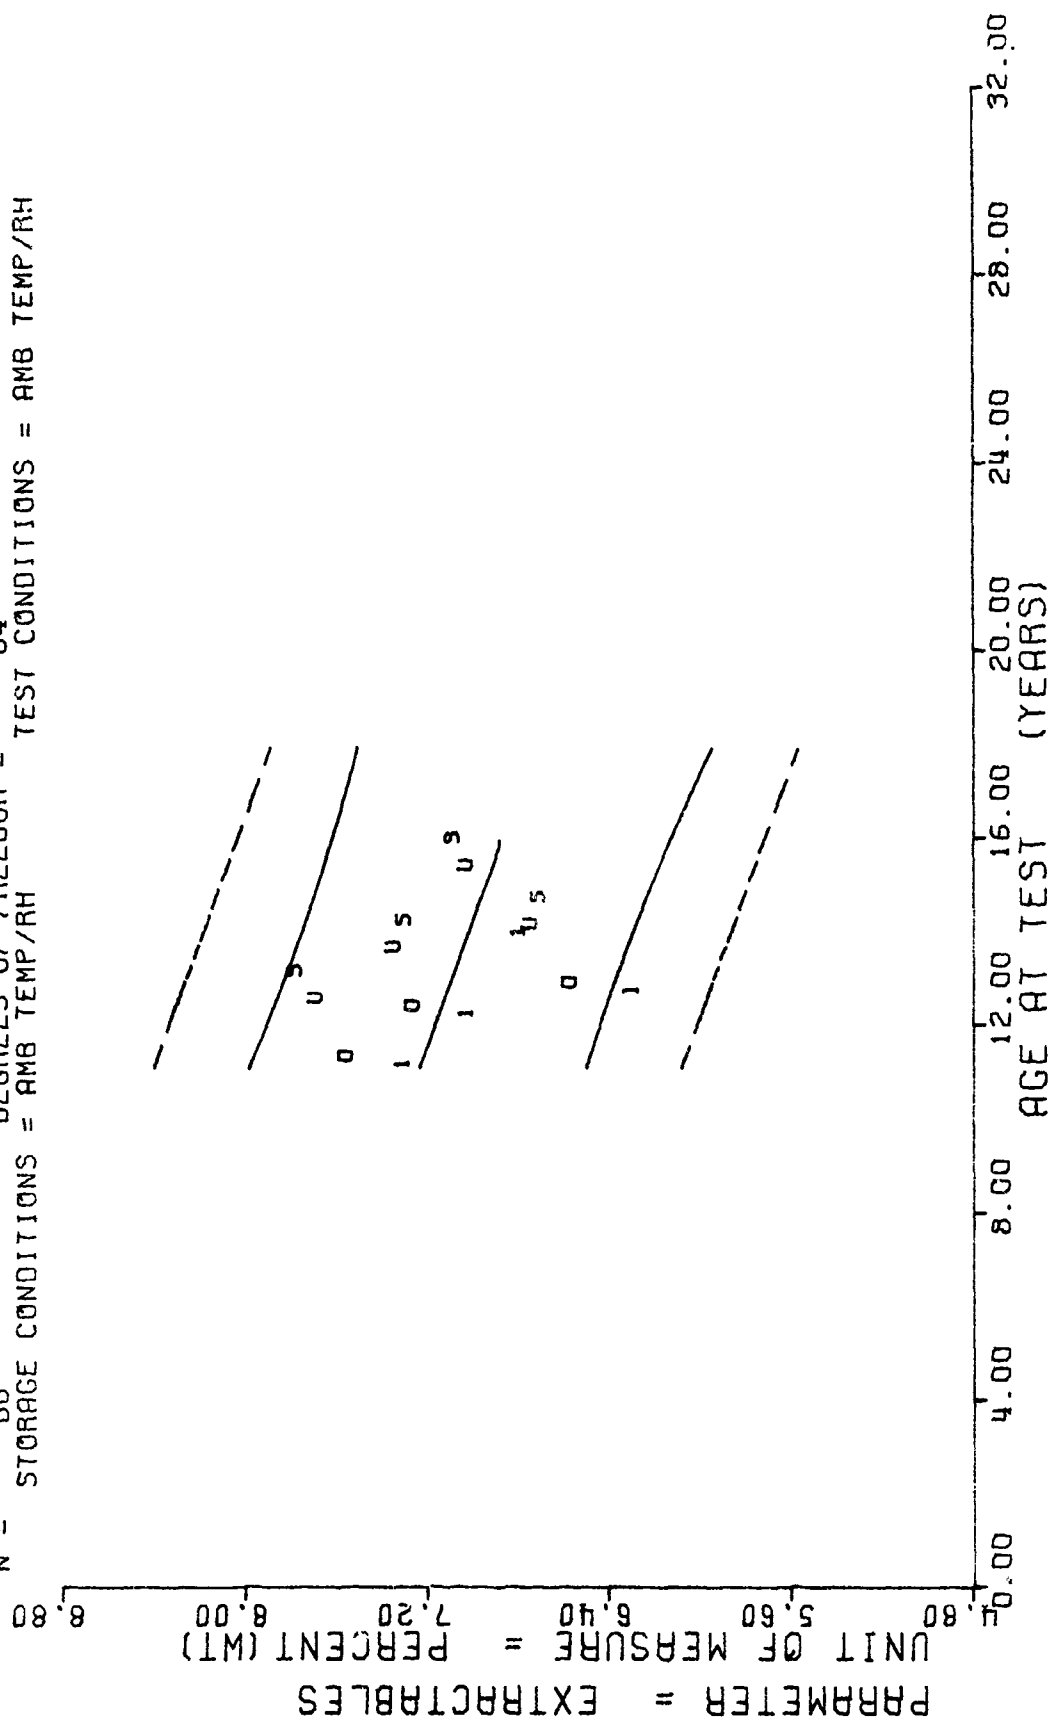


Figure 47

$Y = ((+4.1348895E+00) + (-2.8076343E-03) \times X)$
 $F = +4.8216692E+00$ SIGNIFICANCE OF $F =$ SIGNIFICANT $\sigma_r = +1.8014683E-01$
 $R = -2.6468912E-01$ SIGNIFICANCE OF $R =$ SIGNIFICANT $S_e = +1.2786210E-03$
 $t = +2.1958299E+00$ SIGNIFICANCE OF $t =$ SIGNIFICANT $S_r = +1.7507362E-01$
 $N = 66$ DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

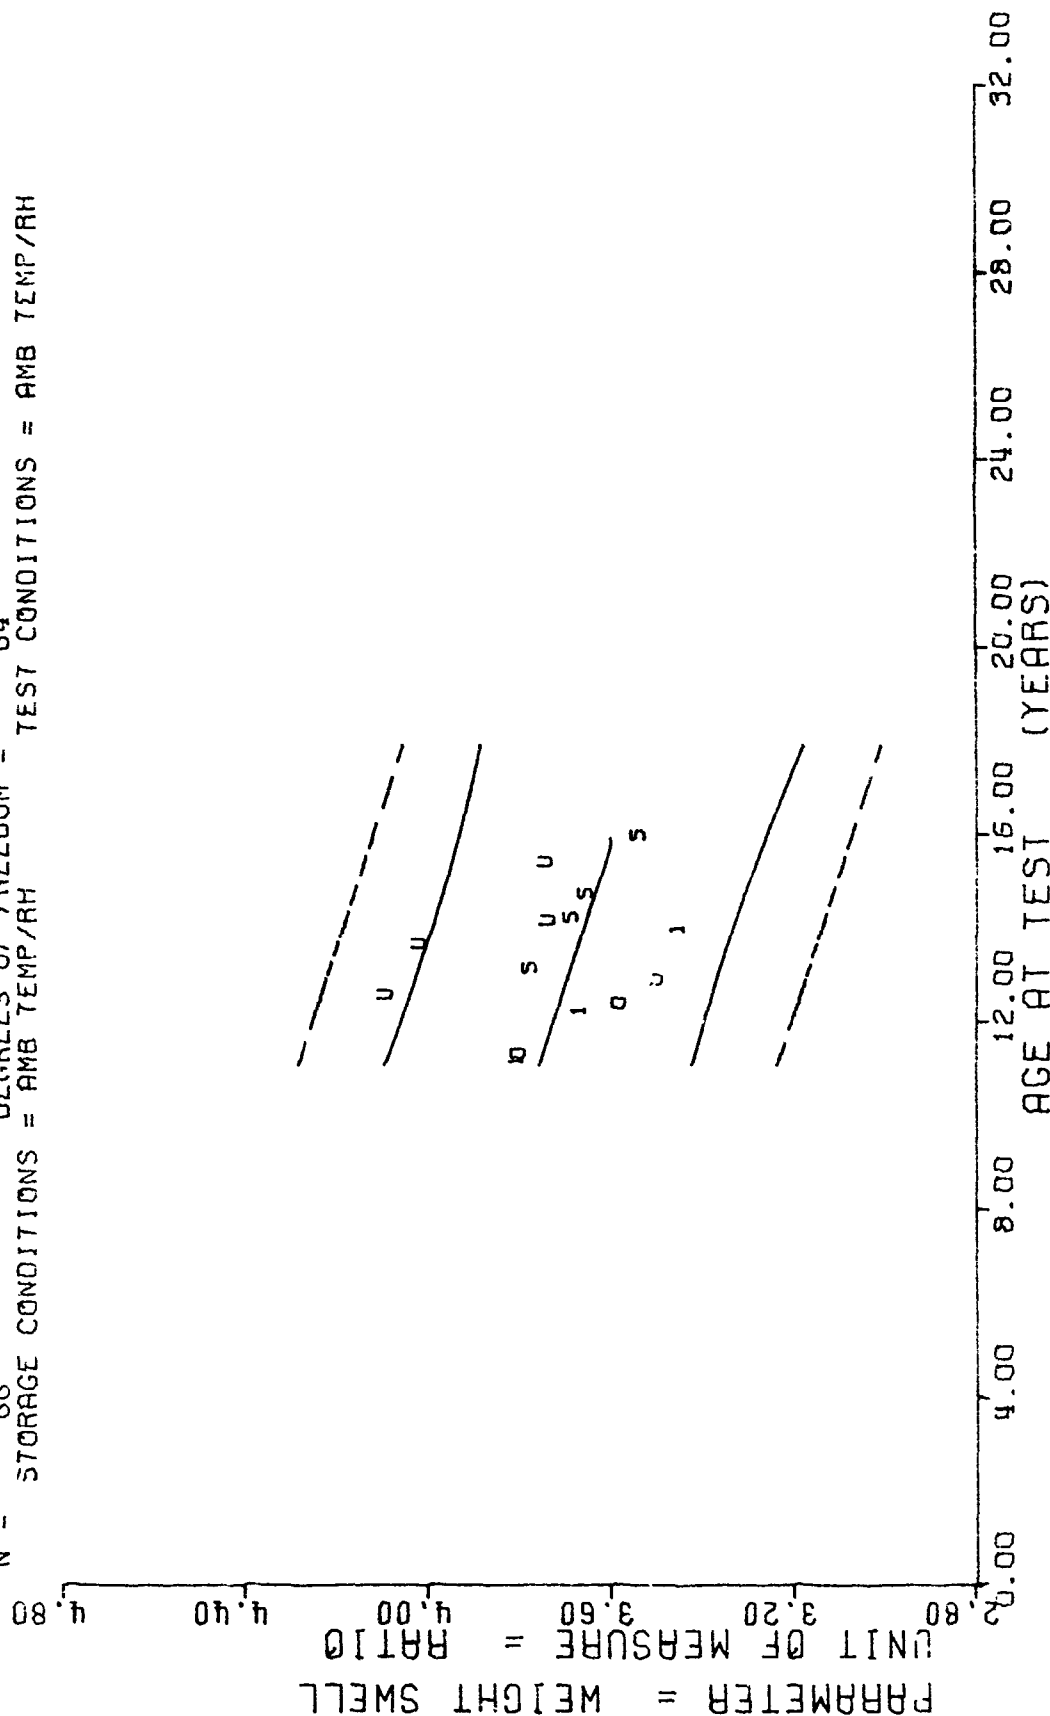

DISSECTED MTR, STAGE 1, TP-H1011, SOL GEL, GEL SWELL RATIO

Figure 48

$Y = ((+1.7975951E+00) + (-1.6099795E-04) * X)$
 F = +6.9785464E+00 SIGNIFICANCE OF F = SIGNIFICANT $\sigma_1 = +8.7201430E-03$
 R = -3.1355875E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +6.0944969E-05$
 t = +2.6416938E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_2 = +8.3448154E-03$
 N = 66 DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH


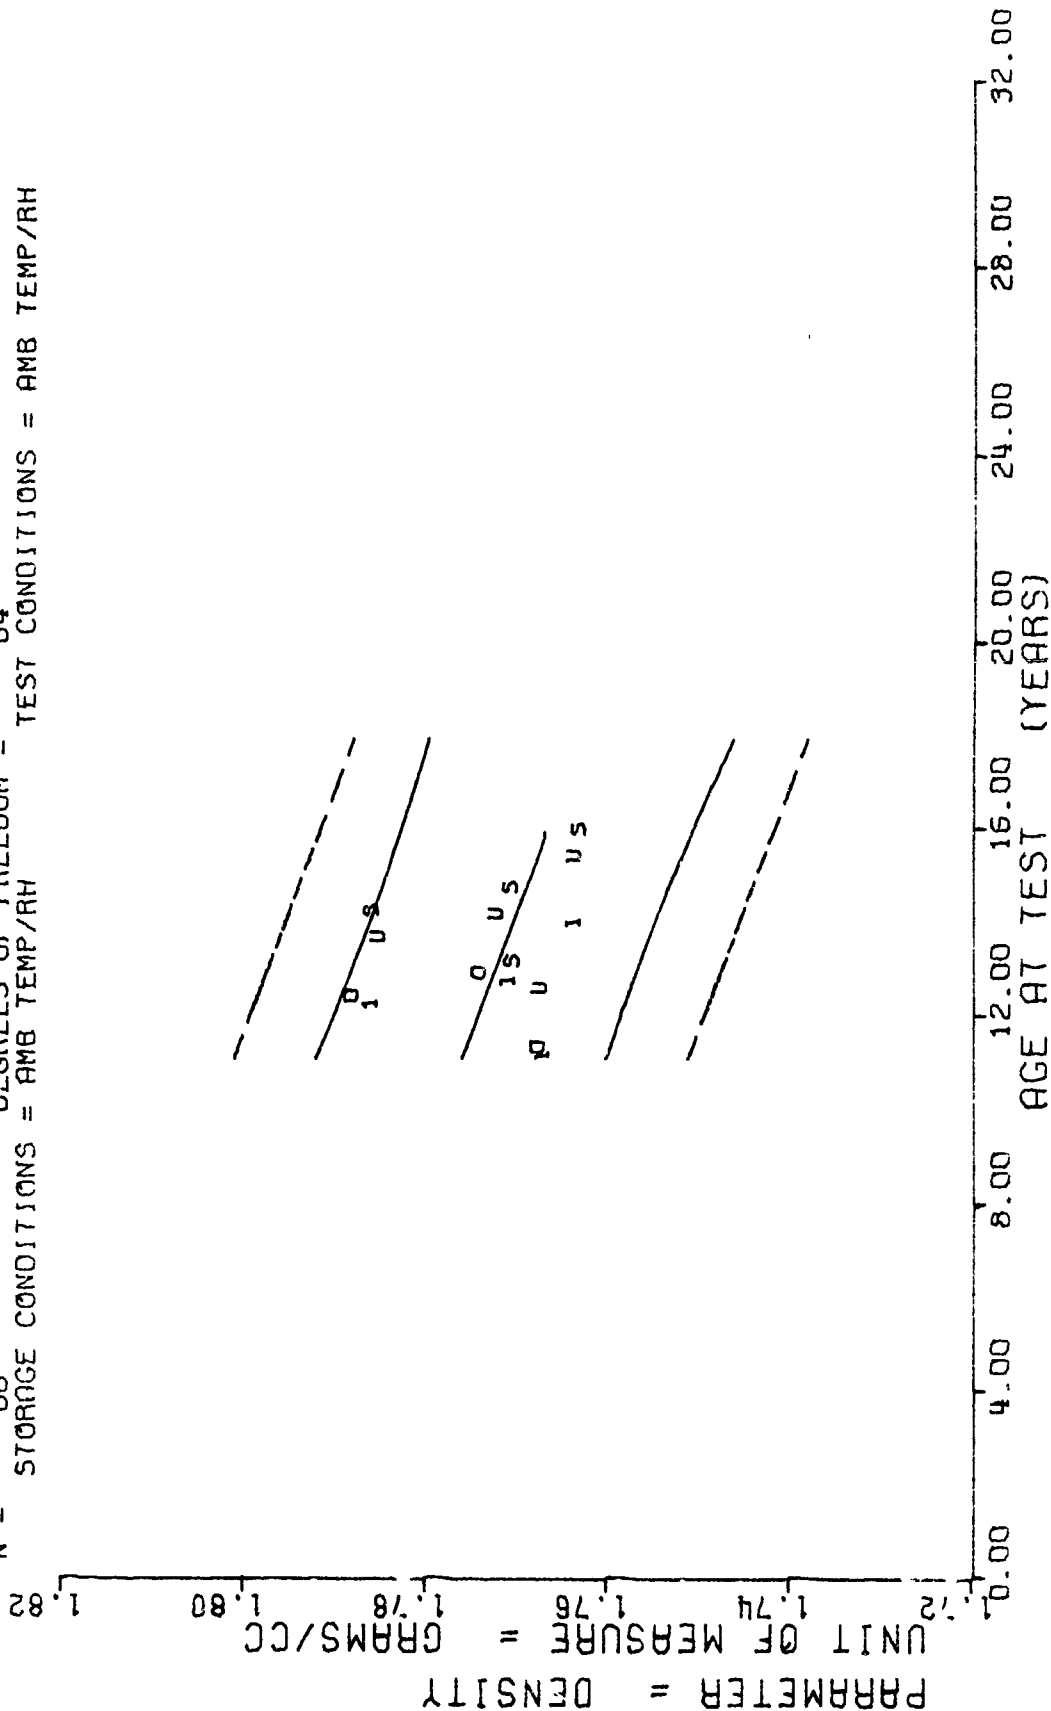


Figure 49


$F = +1.0159758E+01$
 $R = -3.7013277E-01$
 $t = +3.1874376E+00$
 $N = 66$
 $Y = ((+1.6561716E-02) + (-3.7854115E-05) \times X)$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

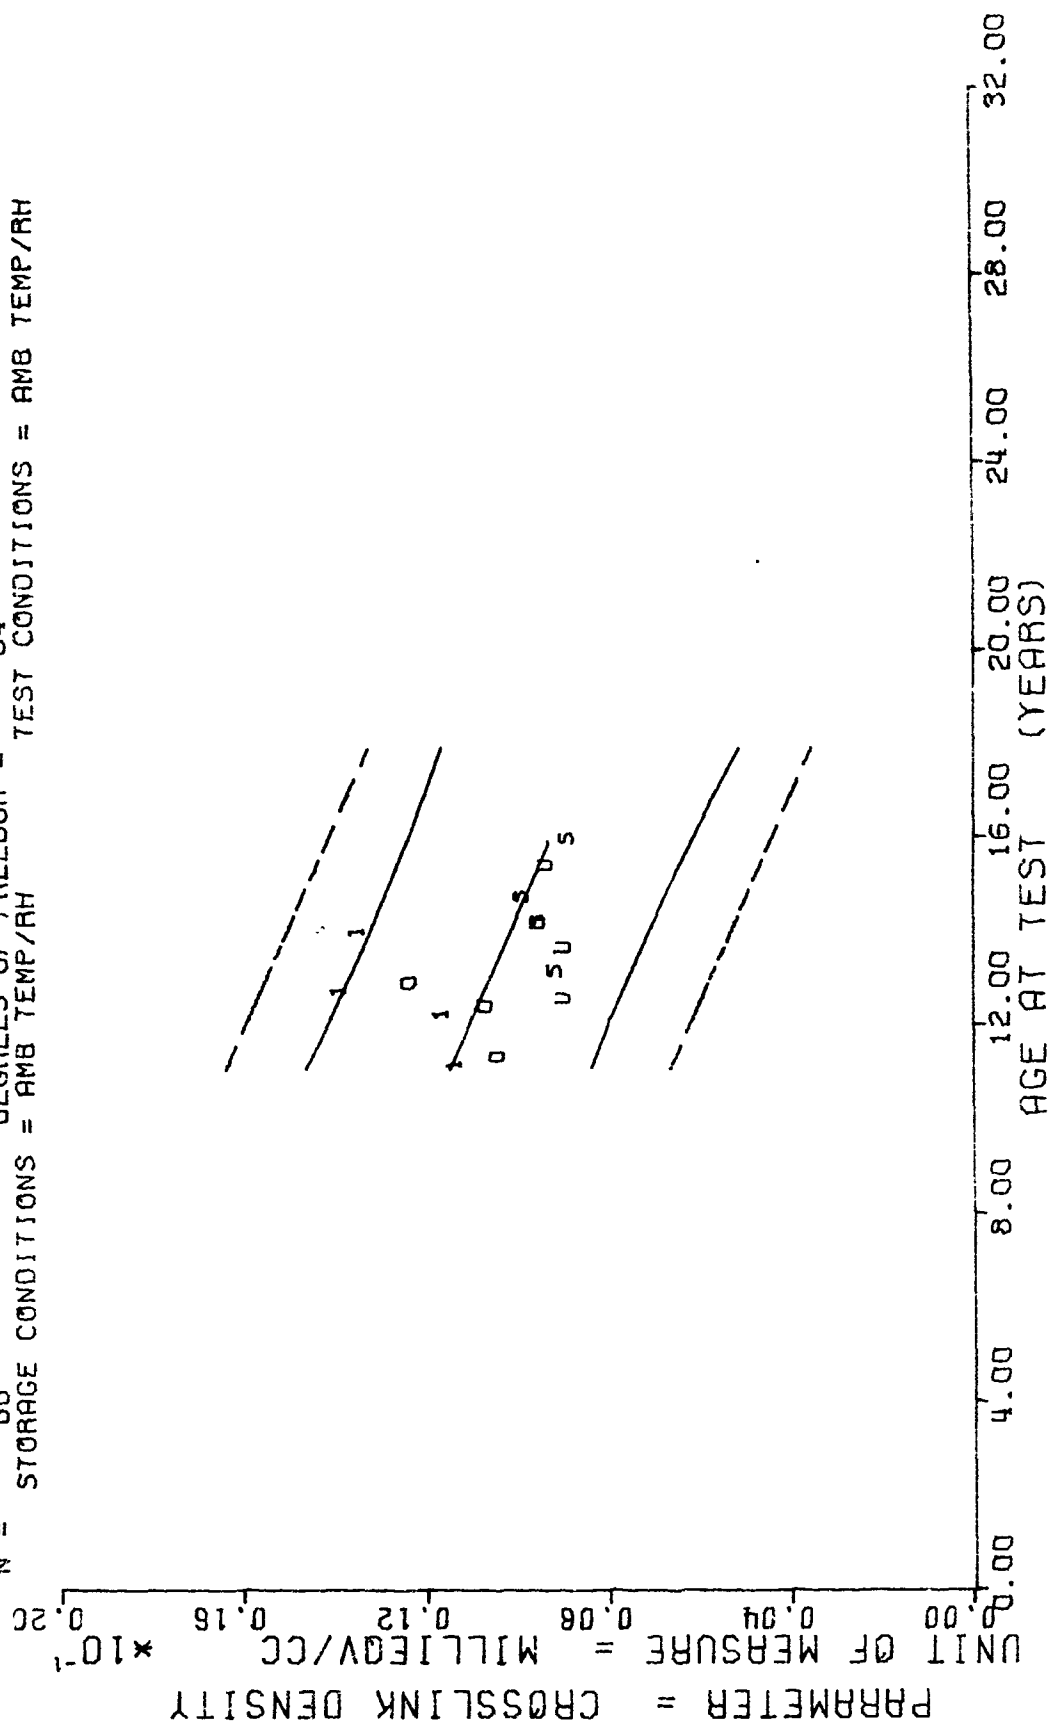

DISSECTED MTR, STAGE 1. TP-H1011, SOL GEL, CROSSLINK DENSITY

Figure 50


TEMPERATURE CORRECTED FAILURE ENVELOPE

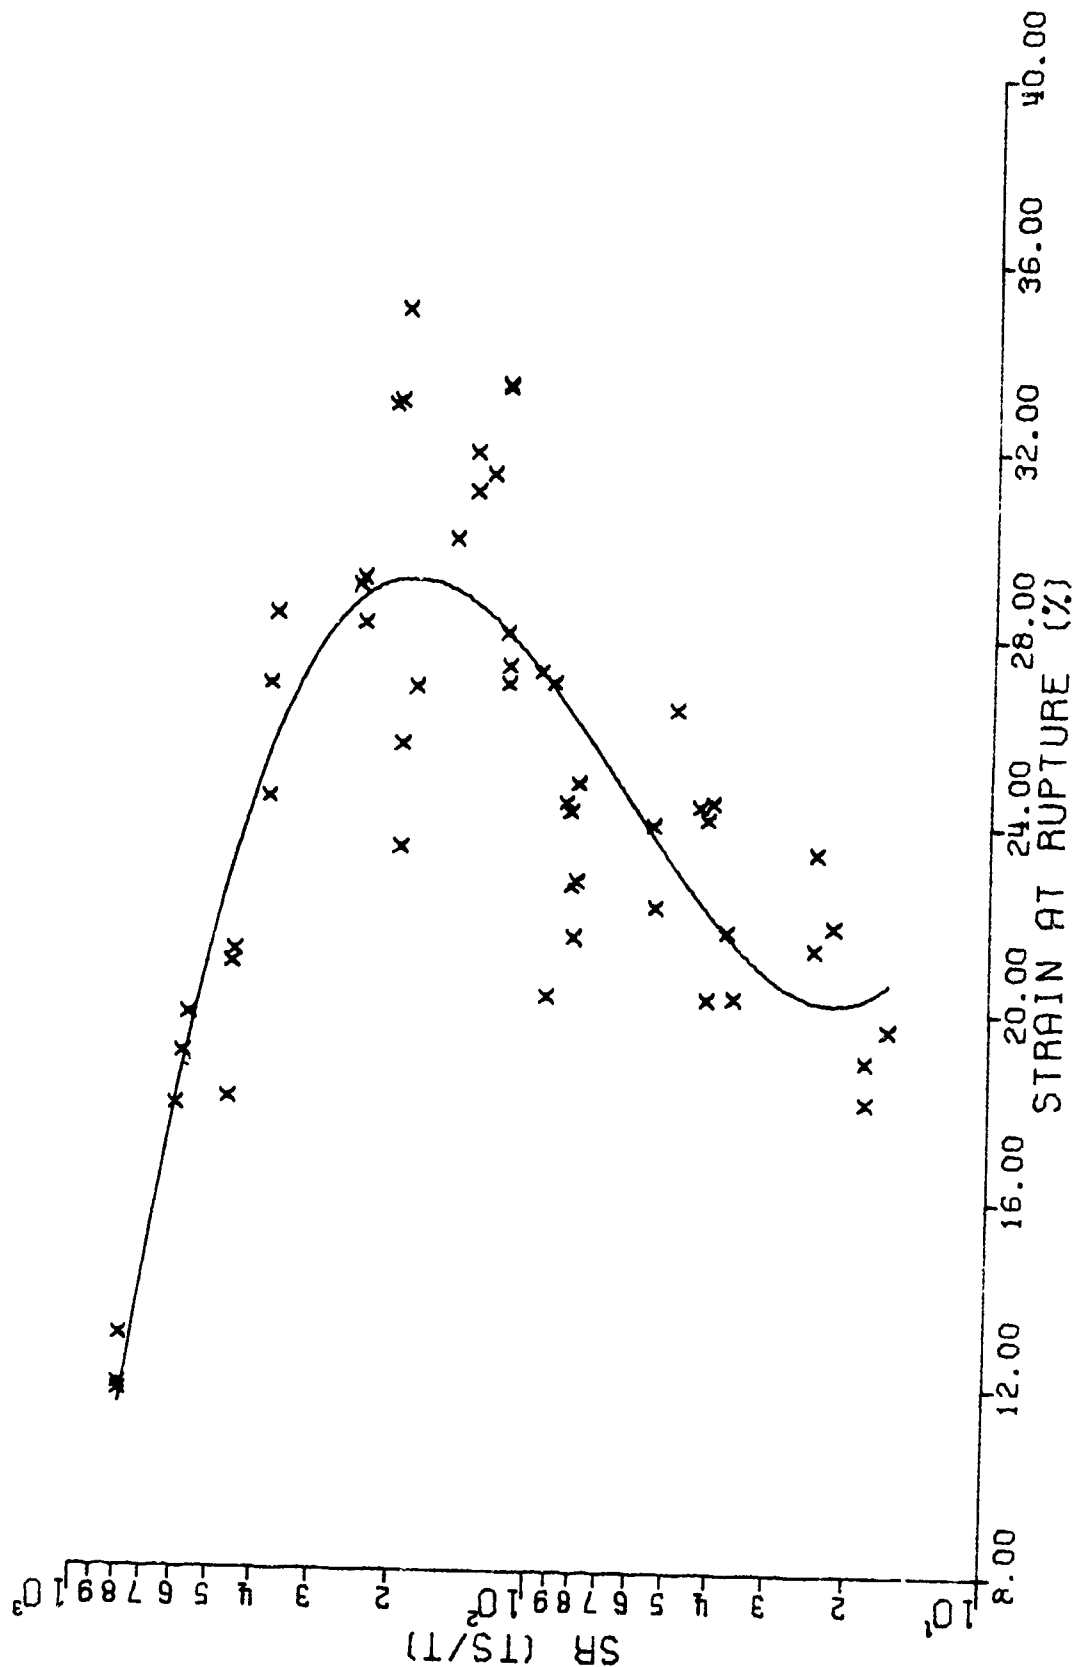

FAILURE ENVELOPE (MOTOR/SN STM-012) DISSECTED MOTOR, STAGE I. 7P-H1011

Figure 51

TEMPERATURE CORRECTED FAILURE ENVELOPE

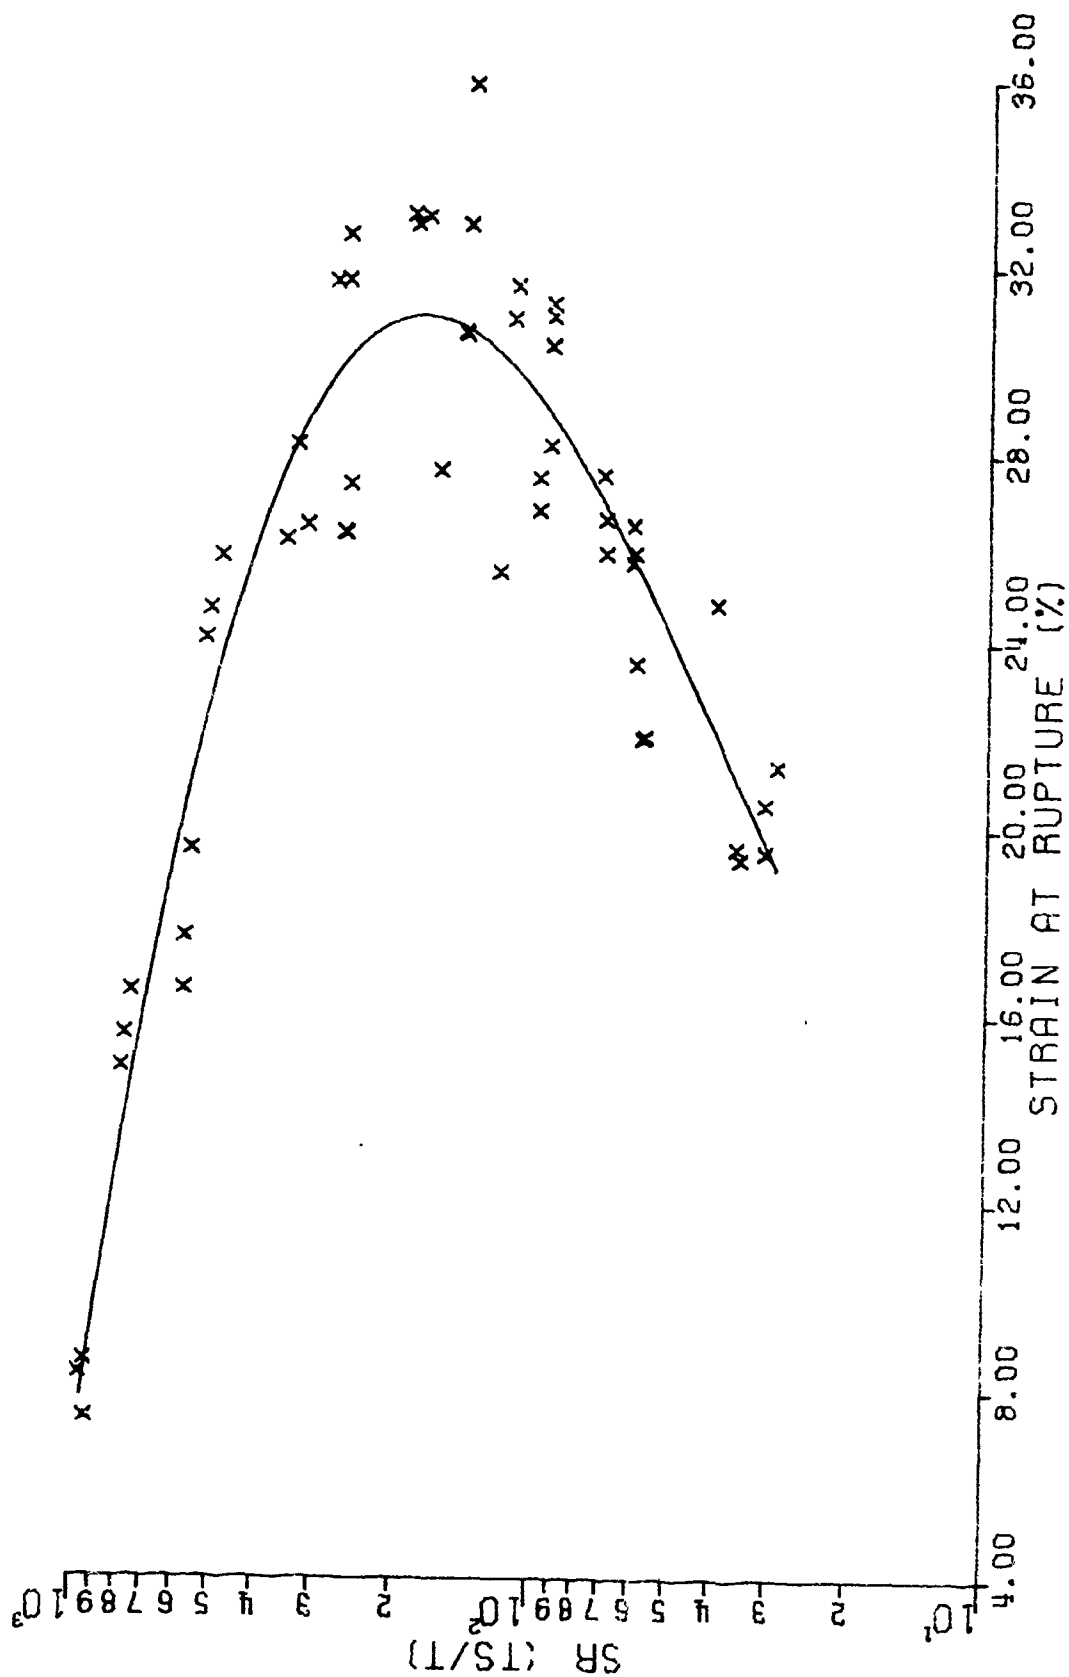

FAILURE ENVELOPE (MOTOR/SN 0012199) DISSECTED MOTOR, STAGE I, TP-H1011

DISTRIBUTION

NR
COPIES

OOALC

MMWRME

1

MMWRMT

1

DIC (TISIR) Cameron Station, Alexandria, VA 22314

2

SAMSO, Norton AFB, CA 92409

MNNP

1

TWR Systems, Norton AFB, CA 92409

Attn: Mr. J. C. Metcalf, Bldg. 523/315

1

AFPRO, Thiokol Chemical Corporation

2

Wasatch Division

P. O. Box 524

Brigham City, UT 84302

(Cy to R. E. Keating)

AFRPL (MKPB) Edwards AFB, CA 93523

1

SAC (LGMB) Offutt AFB, NB 68113

1

U. S. Naval Ordnance Station, Indian Head, MD 20640

1

Attn: Dr. James H. Wiegand

Fleet Support Dept., Propulsion

System Development Division, Code FS7

CPIA, Johns Hopkins University

1

Attn: Dr. P. L. Nichols

Applied Physics Laboratory

Johns Hopkins Road

Laurel, MD 20810

Naval Plant Branch Representative

1

Attn Mr. David W. Pratt

P. O. Box 157, Bacchus Works

Magna, UT 84044

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 392 (78)✓	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Minuteman Stage I Dissected Motor Program		5. TYPE OF REPORT & PERIOD COVERED Test Results - Semi Annual
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) John A. Thompson		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Propellant Lab Section✓ Directorate of Maintenance OO-ALC Hill AFB, UT 84406		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS MMRM Project M82934C- WNL 17514
11. CONTROLLING OFFICE NAME AND ADDRESS Service Engineering Division Directorate of Materiel Management OO-ALC Hill AFB, UT 84406		12. REPORT DATE March 1978
		13. NUMBER OF PAGES 97
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release, Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Minuteman Solid Propellant		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Testing was performed to determine the useful shelf/service life for LGM-30 Stage I Rocket Motors. A three year storage program for propellant and components was started in May 1961. This program was then extended to a ten year study and later continued indefinitely to assure that a deterioration in motor physical characteristics could be detected in time to take some corrective actions before the weapon system performance deteriorated below an acceptable level.		

(over)

This report covers only propellant data and limited case bond data. The malfunction of an environmental chamber destroyed component samples that had originally been part of this testing program (and the inadvertent burning of some motors during dissection reduced the material available for testing). Planned dissection of selected motors in the future will provide samples for continued component testing. Test specimens for this reporting period were obtained from motors STM-012, 0012099, 0012199 and UP-7775 block propellant.

Separate analyses were made on the respective motors and block propellant for the first time in this report and are shown in the regressions. The plotting symbols for each motor and block propellant are listed in the statistical analyses section.

The data from this test period was combined with data from previous testing and entered into the G085 computer for storage, analysis, and regression analysis. From the statistical analysis of all data tested to date, significant degradation of the propellant does not appear likely for at least two years past the oldest data point.

Future testing will be conducted on dissected motors.