

AD-A055 742

ARMY ENGINEER WATERWAYS EXPERIMENT STATION VICKSBURG MISS F/G 11/2  
ALKALI-SILICA REACTION PRODUCTS FROM SEVERAL CONCRETES: OPTICAL--ETC(U)  
MAY 78 A U BUCK, K MATHER  
WES-MP-C-78-7


UNCLASSIFIED

NL

| OF |  
AD  
A055742



END  
DATE  
FILMED  
8 -78  
DDC

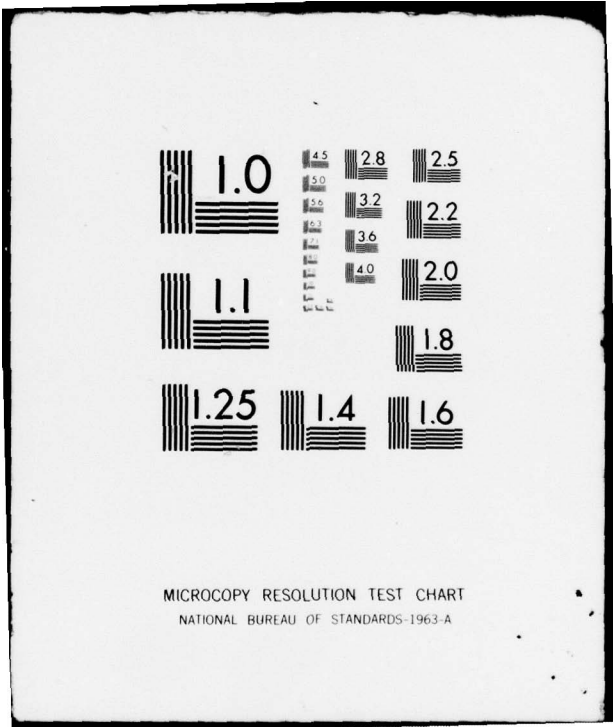

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

FOR FURTHER TRAN *2*

AD A 055742



MISCELLANEOUS PAPER C-78-7

# ALKALI-SILICA REACTION PRODUCTS FROM SEVERAL CONCRETES: OPTICAL, CHEMICAL AND X-RAY DIFFRACTION DATA

by

Alan D. Buck, Katharine Mather


Concrete Laboratory  
U. S. Army Engineer Waterways Experiment Station  
P. O. Box 631, Vicksburg, Miss. 39180

May 1978  
Final Report

Approved For Public Release; Distribution Unlimited

AD No. —  
DDC FILE COPY

DDC  
JUN 23 1978  
ALUSTR

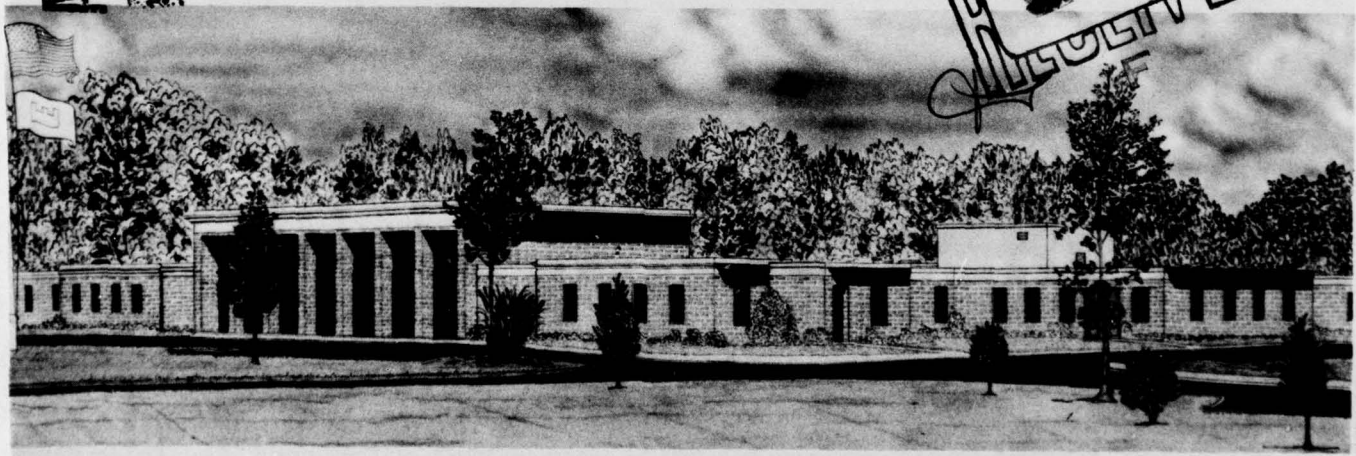

Prepared for Office, Chief of Engineers, U. S. Army  
Washington, D. C. 20314

78 06 21 104

14  
WES-MP-C-78-7  
Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Miscellaneous Paper C-78-7	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) ALKALI-SILICA REACTION PRODUCTS FROM SEVERAL CONCRETES: OPTICAL, CHEMICAL, AND X-RAY DIFFRACTION DATA	5. TYPE OF REPORT & PERIOD COVERED Final report	6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Alan D. Buck Katharine Mather	8. CONTRACT OR GRANT NUMBER(s)	
9. PERFORMING ORGANIZATION NAME AND ADDRESS U. S. Army Engineer Waterways Experiment Station Concrete Laboratory P. O. Box 631, Vicksburg, Mississippi 39180	10. PROGRAM ELEMENT PROJECT, TASK AREA & WORK UNIT NUMBERS 12/18P	
11. CONTROLLING OFFICE NAME AND ADDRESS Office, Chief of Engineers, U. S. Army Washington, D. C. 20314	12. REPORT DATE May 78	
14. MONITORING AGENCY NAME & ADDRESS (If different from Controlling Office)	13. NUMBER OF PAGES 15	15. SECURITY CLASS. (of this report) Unclassified
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES CTIAC Report No. 31		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Alkali silica reactions      Light microscopy Chemical analysis              X-ray diffraction Concretes Gels		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Alkali-silica reaction products from six different concretes were examined by X-ray diffraction and light microscope, and four of the gels were chemically analyzed. Most of the reaction products were crystalline in considerable part and were composed of one or more of four phases. Two of the phases were tentatively identified as variants on CSH(I) and CSH(II).		

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

78 06 21 104  
038-100  
Full

Preface

This paper was prepared for the Fourth International Conference on the "Effect of Alkalies in Cement and Concrete" to be held at Purdue University, West Lafayette, Indiana, 4-8 June 1978.

It was approved for presentation and publication by the Office, Chief of Engineers (OCE). Results in the paper were obtained under the sponsorship of the OCE, three Corps of Engineers Districts, Southeast Division, Bureau of Yards and Docks, U. S. Navy, and Tennessee Valley Authority.

Funds for this edition were provided by the Concrete Technology Information and Analysis Center. This is CTIAC report No. 31.

COL John L. Cannon was Commander and Director of the U. S. Army Engineer Waterways Experiment Station while this paper was prepared. Mr. F. R. Brown was Technical Director.

ACCESSION for	
WHS	White Section <input checked="" type="checkbox"/>
ODC	Buff Section <input type="checkbox"/>
MANUFACTURED	<input type="checkbox"/>
POST-1961 DATE	
BY	
DISTRIBUTION/AVAILABILITY CODES	
DT	SPECIAL
A	

Contents

	<u>Page</u>
Preface . . . . .	1
Introduction . . . . .	3
Age of Specimens . . . . .	3
Reactive Aggregates . . . . .	4
X-Ray Diffraction Data . . . . .	4
Light Microscopy and Chemical Analyses . . . . .	6
Conclusions . . . . .	6
Acknowledgement . . . . .	7
References . . . . .	8
Tables 1-3	

### Introduction

Bryant Mather (1), McConnell, Mielenz, et al (2), (3), and Krogh (4) provided optical or chemical data or both on alkali-silica reaction products. Poole (5) reported electron-probe spot-microanalyses within rims developed on the Beltane opal in specimens containing high-alkali cement, stored at 40°C over water for periods up to 28 days. He found that in a specimen examined after 28 days at 40°C, containing cement with 6% NaCl added at the time of manufacture, there was 45.77% CaO in the reaction-rim material close to the cement interface. In the specimen examined after 7 days at 40°C containing cement with 2% NaCl added during manufacture there was 54.06% of CaO in the reaction-rim material close to the interface. In both specimens calcium had moved through the reaction rim into the opal. These electron-probe microanalyses clearly show the mobility of calcium into the alkali-silica reaction product.

We have collected X-ray diffraction and light microscope data and made chemical analyses of reaction products from six different concretes affected by alkali-silica reaction. We have only four chemical analyses of the reaction products from these six concretes but we believe that the chemical analyses are reliable because every sample was hand-picked by a geologist or a chemist who knew how to recognize alkali-reaction product and understood that it was better to have a small pure sample than a larger contaminated one.

### Age of Specimens

Five of the concretes came from structures ranging in age from 24 to 40 years when the samples were taken. The sixth sample was from a concrete beam prepared in the Concrete Laboratory and stored in seawater near St. Augustine, Florida, for about 2 years. A sample of reaction product from this concrete was examined when the beam was about 3 years old. A fresh reaction product sample, obtained from the beam after an additional 20 years of storage in laboratory air, was examined by X-ray diffraction.

### Reactive Aggregates

The aggregates believed to be reactive in these concretes included three distinct groups. They were: opal; mixtures of quartzite and quartz with or without chert; and granite gneiss.

### X-Ray Diffraction Data

Table 1 shows the X-ray diffraction data for eight samples from the six concretes. There are eight samples because three recognizably different types of gel from the Charleston dry dock (6) concrete were examined separately. X-ray diffraction spacings believed to be due to impurities such as quartz or forms of calcium carbonate are shown in Table 1 with the spacings underlined. The data suggest several dangers and possibilities:

a. We can only comment where we have optical information as well as X-ray diffraction information or several X-ray diffraction patterns on how many phases may be present in the samples, leaving out obvious impurities and characteristic secondary reaction products such as calcite, vaterite, and aragonite. We suspect that most of the "gel" reaction products are mixtures of amorphous alkali-silica gel and slowly crystallizing calcium-silicate hydrates that may contain some alkali.

b. Only the gel from the youngest concrete, about 3 years old, with opal as the reactive constituent (7) was amorphous to X-rays. The gel was still amorphous although some calcite, vaterite, and aragonite had formed when a new specimen was examined by X-ray diffraction after 20 more years of storage in laboratory air.

c. The crystalline materials in the other reaction product samples may consist of three phases. One has long spacings at 0.132 and 0.122 nm. A second has a long spacing at 0.113 to 0.115 nm. The third and most abundant type has a 0.105- to 0.108-nm spacing. All three phases appear in the samples from the Charleston dry dock.

d. An 0.85- to 0.88-nm spacing occurs in five of the seven partly crystalline samples. It is associated with the 0.113- to 0.115-nm peak in two of these cases and with the 0.105- to 0.108-nm peak in two others. This association may mean that the 0.105- to 0.108-nm and the 0.113- to 0.115-nm peaks represent one phase with a variable long spacing and an 0.8<sup>+</sup>-nm spacing. Absence of a longer spacing with the 0.86-nm peak in one case may indicate a situation like that in CSH(I) where the long spacing does not always appear. The 0.85- to 0.88-nm peak may arise from an altogether different phase. This second possibility is considered probable.

The identification of the crystalline materials in the partly crystalline gel from the several concretes is uncertain. A thorough effort to identify the spacings in the diffraction charts of the gel from the New Savannah Bluff Lock and Dam concrete (9) with reactive granite gneiss coarse aggregate led to the possibility that the 0.105- to 0.108-nm material might be jennite (9) or a CSH(II) (14), and the 0.85- to 0.88-nm material tricalcium-silicate hydrate (9). No alkali silicate hydrates fitted. Tricalcium-silicate hydrate has been prepared by autoclaving at 200°C and is not known to have been reported from normal ambient temperature material. However time may proxy for temperature in some reactions, and it may be easier for a calcium-silicate hydrate to crystallize within an amorphous flexible alkali-silica gel than in a cement paste. Table 1 does show in almost all the samples the three familiar spacings at 0.307, 0.282, 0.182-nm, that appear in well hydrated cement paste. However in these patterns there are many other lines, usually representing substances less crystalline than quartz (the universal contaminant) but as well crystallized as most of the constituents of anhydrous portland cement.

These diffraction patterns show a gel-like hump, suggesting that the important part of the compositions including Na<sub>2</sub>O, K<sub>2</sub>O, part of the SiO<sub>2</sub>, and part of the water remain as gels or the equivalent to hydrated glasses.

If Table 1 contains items that seem recognizable to people who see it, we would very much appreciate some discussion from any of them.

### Light Microscopy and Chemical Analyses

The light microscope and chemical results in Tables 2 and 3 complete the information that we have on the reaction products in these six concretes affected by alkali-silica reaction. We always look for gel in concrete suspected of alkali-silica reaction since if gel is present it is unequivocal evidence that the reaction took place, and therefore have considerable familiarity with appearance of gel in immersion mounts in plane light, and with crossed polarizers, and have determined a number of indices of refraction of gel. We are also very familiar with gel viewed using the stereomicroscope. We also usually analyze the reaction products to assure that they contain considerable  $\text{SiO}_2$  and some alkali. No determination of alkalies was made on the samples from Oliver Lock probably because we did not yet have a flame photometer.

### Conclusions

Our tentative conclusions are as shown below. It appears that alkali-silica reaction product in its early stages contains very little calcium, a high concentration of silica, and more total alkali than calcium (Table 3, Beam 1850). Calcium moves into the product from the large supply available in the cement paste and calcium hydroxide, but moves at varying rates over unknown distances. Examination of concrete thin sections, comparing sections of normal concrete and that affected by alkali-silica reaction, shows that crystalline  $\text{Ca(OH)}_2$  is depleted in parts of the mortar where reaction has proceeded.

Ultimately, at ages in field structures at least as low as 24 years (Table 1, Charleston Naval Dry Dock No. 2) complex products develop. They include products giving X-ray diffraction spacings that suggest that part at least of the products is related to CSH(I) (13) and possibly to CSH(II) (14). CSH(I) and CSH(II) both have variable long spacings. It may be a consequence of the composition of these complex, probably mixed, products that they differ from sample to sample in their crystalline parts but share a family resemblance. This similarity which exists regardless of

the type of reactive aggregate, with the possible exception of opal, suggests that the same mechanism is involved in five of the cases discussed here. This in turn suggests that division of silica bearing aggregates into those that participate in the alkali-silica reaction and those that participate in an alkali-silicate reaction may be a misleading practice.

#### Acknowledgment

The tests described and the resulting data presented herein, unless otherwise noted, were obtained from research conducted under the Civil Works Research and Development Program of the United States Army Corps of Engineers by the U. S. Army Engineer Waterways Experiment Station. Permission was granted by the Chief of Engineers to publish this information.

### References

- (1) Mather, Bryant, Cracking of Concrete in the Tuscaloosa Lock, Highway Research Board Proc Thirty-First Annual Meeting, 1952, pp 218-233.
- (2) McConnell, D.; Mielenz, R. C.; Holland, W. Y.; and Greene, K. T.; Cement Aggregate Reaction in Concrete, Proc. Am. Conc. Inst. vol 44, Journal ACI vol 19 No. 2, pp 93-128.
- (3) McConnell, D.; Mielenz, R. C.; Holland, W. Y.; and Greene, K. T.; Petrology of Concrete Affected by Cement-Aggregate Reaction, The Geological Society of America, Engineering Geology (Berkey) Volume, Nov. 1950, pp 225-250.
- (4) Krogh, Hanne, Examination of synthetic alkali-silica gels, pp 131-163, Symposium on Alkali-Aggregate Reaction: Preventive Measures, Reykjavik, August 1975, The Building Research Institute, Keldnaholt/Reykjavik, Iceland.
- (5) Poole, A. B.; Electron Probe Microanalyses of reaction zones at cement/opal interfaces, The Effect of Alkalies on the Properties of Concrete, Proceedings of a Symposium Held in London, Sept. 1976.
- (6) Buck, Alan D.; and Mather, Katharine; Concrete Cores from Dry Dock No. 2, Charleston Naval Shipyard, S. C., Miscellaneous Paper C-69-6, U. S. Army Engineer Waterways Experiment Station, Vicksburg, Miss. 39180, USA.
- (7) Buck, A. D., Seawater Exposure Tests, Alkali-Aggregate Reactivity; draft report, U. S. Army Engineer Waterways Experiment Station, Concrete Laboratory, June 1958.
- (8) Buck, Alan D., Tests of Concrete Core, Fort Meade, Md., 21 January 1977; letter report to U. S. Army Engineer District, Baltimore, Md.
- (9) Buck, A. D., Tests of Cores from New Savannah Bluff Lock and Dam, 18 October 1977; letter report to U. S. Army Engineer District, Savannah, Ga.
- (10) Mather, K. and B., Disintegration of Concrete from Tuscaloosa Lock and Dam, U. S. Army Engineer Waterways Experiment Station, 25 August 1949.

- (11) McDonald, J. E.; Campbell, Roy L.; An Investigation of Concrete Condition, William Bacon Oliver Lock and Spillway, Miscellaneous Paper C-77-5, June 1977, U. S. Army Engineer Waterways Experiment Station, Vicksburg, Miss. 39180.
- (12) Buck, Alan D.; and Mather, Katharine; Examination of Fontana Dam Concrete Cores, 3 May 1974; letter report to Tennessee Valley Authority.
- (13) Taylor, H. F. W., The Calcium Silicate Hydrates, Proc. International Symposium on the Chemistry of Cement, Tokyo, 1968, The Cement Association of Japan, Dec. 31, 1969, vol II, pp 1-26.
- (14) Gard, J. A.; and Taylor, H. F. W.; Calcium Silicate Hydrate (II) (C-S-H(II)), Cement and Concrete Research, vol 6, pp 667-678, 1976.



Table 1 (Continued)

		Charleston Naval Dry Dock No. 2																	
		New Savannah			Oliver Lock			Fontana Dam			From 1/4-in. Void			Tan, Layered, Translucent Gel		Composite for Chemical Analysis		Beam No. 1850	
		Bluff L and D			38 Years			33 Years			24 Years			VI		VII** +		3 and 23 Years	
		40 Years			III†			IV** +			V** +			d		VIII** +		d	
		I**			d			d			d			d		d		d	
Fort Meade	I																		
45 Years	d	0.299	m		0.298	w				0.298	w				0.300	w			
					0.293	m				0.290	m				0.293	m			
					0.290	m				0.283	w				0.289	m			
					0.282	w				0.283	w				0.282	w			
					0.276	v				0.279	v				0.274	v			
					0.272	m				0.274	v				0.271	w			
					0.270	w				0.261	v				0.261	v			
					0.263	w				0.261	v				0.253	v			
					0.255	w				0.245	w				0.245	w			
					0.248	v				0.241	v				0.245	w			
					0.245	w				0.229	w				0.232	v			
					0.228	m				0.223	v				0.228	v			
					0.223	w				0.221	v				0.223	w			
					0.215	v				0.221	v				0.213	v			
					0.212	s				0.212	v				0.206	v			
					0.209	v				0.209	v				0.200	v			
					0.206	m				0.206	w				0.198	v			
					0.197	m				0.198	w				0.198	v			
					0.191	v				0.192	m				0.187	v			
					0.188	w				0.188	w				0.183	v			
					0.183	w				0.184	w				0.183	v			
					0.182	s				0.182	w				0.182	w			
					0.181	w				0.181	w				0.182	w			
					0.207	v				0.207	v				0.207	v			
					0.198	w				0.198	w				0.198	v			
					0.188	w				0.188	w				0.188	v			
					0.183	w				0.183	w				0.183	v			
					0.182	s				0.182	w				0.182	w			
					0.181	w				0.181	w				0.181	w			

(Continued)



Table 2  
Light Microscope Data on Alkali-Silica  
Reaction Products from Six Concretes\*

<u>Source of Gel</u>	<u>Description of Gel</u>
Fort Meade (8)	Clear to brownish in plane light. With crossed polarizers, crystalline material black, gray, and white in a texture like finely granular chert. Amorphous material also present. n < 1.520
New Savannah Bluff Lock and Dam (9)	Apparently crystalline with crossed polarizers, texture like finely granular chert. n = 1.460 - 1.500
Oliver Lock (10)(11)	White to translucent bluish, laminated, often with shrinkage cracks, brittle where dry. Also in pockets and lining cracks, clear to translucent, rubbery to brittle; usually the outer shell of the lining if two varieties are present in one void. By microscope, there were three varieties: with crossed polarizers one anisotropic, with aggregate polarization, low birefringence, and wavy extinction with a misshapen black cross as in strained glass; the second with crossed polarizers had a very fine-grained pepper and salt appearance resembling chert or fine grained calcium hydroxide; the third variety was clear, isotropic, with fewer inclusions than the other types. Ranges of indices of refraction: pepper and salt type n = 1.478 to n = 1.511; in the type with aggregate polarization n = 1.480 to n = 1.502; isotropic gel formed after the cores were drilled n = 1.465 to n = 1.487. The 1976 samples were similar.
Fontana Dam (12)	Semicrystalline; first order gray birefringence in crossed polarized light. n < 1.480  Salt and pepper type in crossed polarized light. 1.482 > n < 1.502  Alternating growth layers of clear and of tan translucent gel; some of the clear material is amorphous. 1.480 > n < 1.520

(Continued)

Table 2 (Concluded)

Source of Gel	Description of Gel
Charleston Dry Dock (6) Gel from 1/4-in. void	Transparent in plane light, crystalline salt and pepper texture with crossed polarizers. $n$ about 1.494
Tan layered gel	Layered structure with fibers normal to layers; fibers appear to be uniaxial +; $1.510 < n < 1.544$
Composite	Amorphous and crystalline material in clear and brownish fragments.
Beam 1850 (7)	Amorphous with $1.460 < n < 1.500$

---

\* See Table 1 for type of aggregate.

Table 3

## Chemical Analyses of Alkali-Silica Reaction Products from Four Concretes

Constituents, Percent by Weight	Oliver Lock		Fontana Dam		Charleston Dry Dock		Beam 1850	
	Sample 1*	Sample 2**	33 Years	33 Years	24 Years	24 Years	3 Years	3 Years
SiO <sub>2</sub>	49.82	61.73	50.70	50.70	66.00	66.00	85.91	85.91
Al <sub>2</sub> O <sub>3</sub>	1.15	2.17	not determined	not determined	1.88†	1.88†	not determined	not determined
Fe <sub>2</sub> O <sub>3</sub>	0.81	0.47	not determined	not determined	not determined	not determined	not determined	not determined
CaO	21.11	12.28	4.76	4.76	11.54	11.54	1.25	1.25
SO <sub>3</sub>	0.16	0.00	not determined	not determined	not determined	not determined	not determined	not determined
Cl <sup>-</sup>	not de- termined	not de- termined	not determined	not determined	0.39	0.39	not determined	not determined
Na <sub>2</sub> O	not de- termined	not de- termined	6.75	6.75	1.30	1.30	2.41	2.41
K <sub>2</sub> O	not de- termined	not de- termined	6.68	6.68	19.00	19.00	0.60	0.60
Insoluble residue	5.58	8.1	not determined	not determined	not determined	not determined	not determined	not determined
Moisture loss at 105°C	34.6	9.81	not determined	not determined	not determined	not determined	5.22	5.22
Moisture loss at 200°C	--	--	not determined	not determined	not determined	not determined	3.09	3.09
Moisture loss at 450°C	--	--	not determined	not determined	17.23	17.23		
Ignition loss	--	14.84	24.80 at 550°C	24.80 at 550°C	not determined	not determined		

\* Scraped from the wall of the 36-in. core hole 16-19 June 1948.

\*\* Collected from pockets in cores from holes 20-1 and 60-1 after cores dried in laboratory air. Analyses made in 1948 and 1949.

† Assumed to be Al<sub>2</sub>O<sub>3</sub> but contained at least some iron. Structure was 10 to 11 years old.

In accordance with letter from DAEN-RDC, DAEN-ASI dated 22 July 1977, Subject: Facsimile Catalog Cards for Laboratory Technical Publications, a facsimile catalog card in Library of Congress MARC format is reproduced below.

Buck, Alan D

Alkali-silica reaction products from several concretes: Optical, chemical, and X-ray diffraction data / by Alan D. Buck, Katharine Mather. Vicksburg, Miss. : U. S. Waterways Experiment Station ; Springfield, Va. : available from National Technical Information Service, 1978.

9, [6.] p. : 27 cm. (Miscellaneous paper - U. S. Army Engineer Waterways Experiment Station ; C-78-7)

Prepared for Office, Chief of Engineers, U. S. Army, Washington, D. C.

CTIAC Report No. 31.

References: p. 8-9.

1. Alkali silica reactions. 2. Chemical analysis. 3. Concretes. 4. Gels. 5. Light microscopy. 6. X ray diffraction. I. Mather, Katharine, joint author. II. United States. Army. Corps of Engineers. III. Series: United States. Waterways Experiment Station, Vicksburg, Miss. Miscellaneous paper ; C-78-7. TA7.W34m no.C-78-7