AD-A057 422 BOEING AEROSPACE CO SEATTLE WASH F/G 1/3
COST ALUMINUM STRUCTURES TECHNOLOGY, PHASE III (CAST).(U)
JAN 78 D GOEHLER F33615-76-C-3111
UNCLASSIFIED D180-22807-1 AFFDL-TR-78-7 NL

1 OF 2
ADA
057422

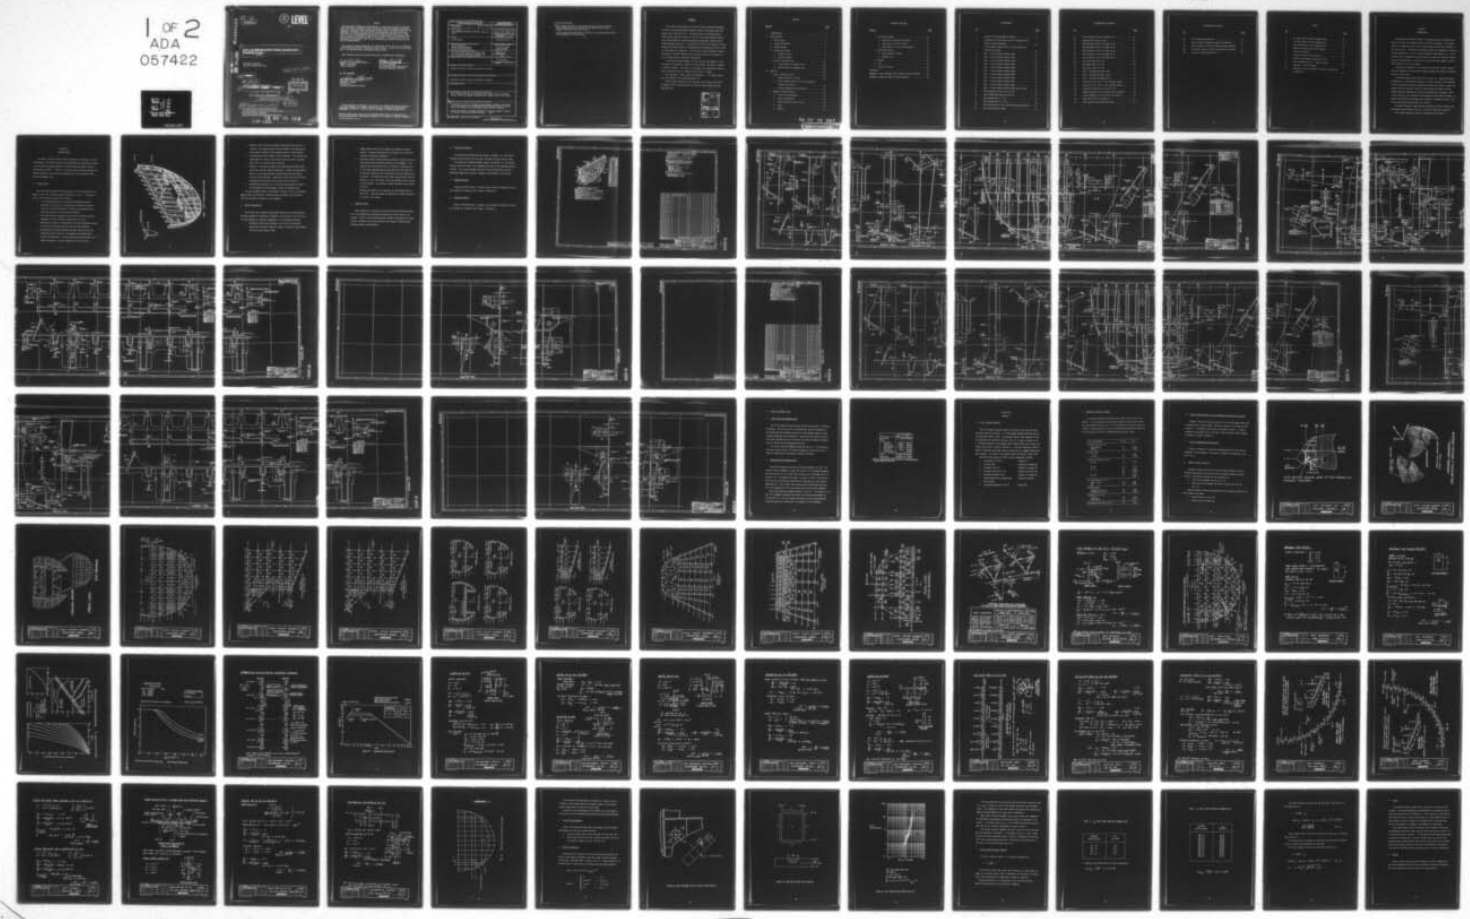

AD A057422
DDC FILE COPY
AD NO.

(18) (19) AFFDL-TR-78-7

(2) LEVEL II

(6) CAST ALUMINUM STRUCTURES TECHNOLOGY, PHASE III (CAST).

NH

THE BOEING COMPANY
SEATTLE, WASHINGTON 98124

(14) D180-22807-1

(11) JAN [redacted] 78

(12) 135 p.

TECHNICAL REPORT AFFDL-TR-78-7
(9) Final Report [redacted] Feb [redacted] – Dec [redacted] 77

DDC
RECEIVED
AUG 15 1978
B

(10) Donald Goehler

Approved for public release; distribution unlimited.

(15) F33615-76-C-3111 (16) 4864

AIR FORCE FLIGHT DYNAMICS LABORATORY
AIR FORCE WRIGHT AERONAUTICAL LABORATORIES 63211F
AIR FORCE SYSTEMS COMMAND
WRIGHT-PATTERSON AIR FORCE BASE, OHIO 45433

78 07 28 043
059 640
mt

NOTICE

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

This report has been reviewed by the Information Office (OI) and is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nations.

This technical report has been reviewed and is approved for publication.

John R. Williamson

JOHN R. WILLIAMSON
Project Engineer,

William R. Johnston

WILLIAM R. JOHNSTON
Actg Prog Mgr, AMS Program Office
Structural Mechanics Division

FOR THE COMMANDER

Holland B. Lowndes

HOLLAND B. LOWNDES
Acting Chief
Structural Mechanics Division

"If your address has changed, if you wish to be removed from our mailing list, or if the addressee is no longer employed by your organization please notify AFFDL/FBA *,W-PAFB, OH 45433 to help us maintain a current mailing list".*

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

AIR FORCE/56780/7 June 1978 — 250

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE	READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER: AFFDL-TR-78-7	2. GOVT ACCESSION NO. / 3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle): CAST ALUMINUM STRUCTURES TECHNOLOGY, PHASE III (CAST)	5. TYPE OF REPORT & PERIOD COVERED: February 1977-December 1977
	6. PERFORMING ORG. REPORT NUMBER: D180-22807-1
7. AUTHOR(s): Donald Goehler	8. CONTRACT OR GRANT NUMBER(s): F33615-76-C-3111
9. PERFORMING ORGANIZATION NAME AND ADDRESS: The Boeing Company, Boeing Aerospace Company, Seattle, Washington 98124	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS: Project No. 486U, Work Unit 486U
11. CONTROLLING OFFICE NAME AND ADDRESS: Air Force Flight Dynamics Laboratory (FBA), Air Force Wright Aeronautical Laboratories, AFSC, Wright-Patterson AFB, OH 45433	12. REPORT DATE: January 1978
	13. NUMBER OF PAGES: 102
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report): Unclassified
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release, distribution unlimited.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

Approved for public release, distribution unlimited.

18. SUPPLEMENTARY NOTES

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

CAST, aluminum castings, YC-14 bulkhead, A357 aluminum alloy, allowables, fatigue, durability, damage tolerance, detail design, static loads, stress

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

The objective of CAST is to establish the necessary structural and manufacturing technologies and to demonstrate the validate the integrity, producibility, and viability of cast aluminum primary airframe structures.

The baseline design is the AMST prototype YC-14 and the component selected was the Nose Landing Gear Support Bulkhead. (Over)

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

Block 20 (Continued)

Detail design activities are described that were aimed at providing a cast bulkhead design for production with no weight penalty and at a minimum of 30% acquisition cost savings.

A detail design was completed that resulted in a 6.5-pound weight savings and an estimated 37.7% cost saving.

FOREWORD

This report was prepared by the Boeing Military Airplane Development Division of the Boeing Aerospace Company, Seattle, Washington under USAF Contract No. F33615-76-C-3111. The contract work was performed under project 486U under the direction of the Air Force Flight Dynamics Laboratory, Advanced Metallic Structures/Advanced Development Program Office, Wright-Patterson AFB, Ohio. A significant portion of the contract is being funded by the Metals Branch of the Manufacturing Technology Division of the Air Force Materials Laboratory. The Air Force Project Engineer is John R. Williamson of the AMS Program Office, Structural Mechanics Division, Air Force Flight Dynamics Laboratories (AFFDL/FBA).

The Boeing Aerospace Company, Military Airplane Development, is the contractor, with Donald E. Strand as Program Manager and Donald D. Goehler as Technical Leader. This phase of the program was conducted by Richard C. Jones assisted by Carlos J. Romero and Christian K. Gunther.

The contractor's report number is D180-22807-1. This report covers work from February 1977 through December 1977.

Previous work conducted on this contract over the period June 1976 to February 1977 has been reported in Technical Report AFFDL-TR-77-36, dated May 1977.

A043 469

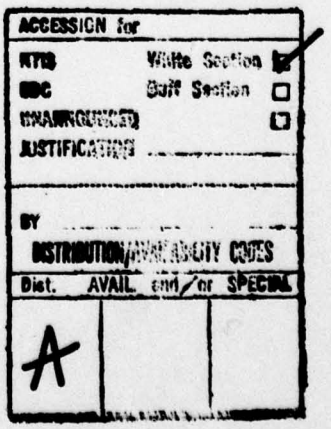

CONTENTS

Section			Page
I.	INTRODUCTION		1
II.	DETAIL DESIGN		2
	1.	Design Layout	3
	2.	Design Coordination	4
	3.	Drawing Release	5
	4.	Production Drawings	6
		a. Bulkhead Casting	6
		b. Bulkhead Assembly	6
	5.	Baseline Component Data	19
		a. Initial Baseline Component Data	19
		b. Updated Baseline Component Data	19
III.	ANALYSIS		21
	1.	Static Strength Analysis	21
		a. Summary--Margins of Safety	22
		b. Finite Element Analysis of Cast Bulkhead and Transition Structure	23
		c. Critical Components Stress Analysis	23
	2.	Damage Tolerance Analysis	23
		a. Initial Flaw Assumption	59
		b. Material Properties	59
		c. Stress Intensity Factor Solution	63
		d. Loads	67
		e. Results	67

78 07 28 043

PRECEDING PAGE BLANK-NOT FILMED

CONTENTS (Continued)

Section		Page
3.	Sensitivity Studies	70
	a. Sensitivity to Material Properties	71
	b. Sensitivity to Aircraft Usage	74
	c. Sensitivity to Initial Flaw Assumption	74
4.	Durability Analysis	76
	a. Detail Design S-N Curves	78
	b. Economic Life	83
5.	Weights	88
6.	Cost	88
7.	Effects of Defects	91
REFERENCES		95
APPENDIX A--LOAD ATTACHMENT POINT A ANALYSIS STRESS SPECTRUM		96
APPENDIX B--SHEAR WEB ANALYSIS STRESS SPECTRUM		102

ILLUSTRATIONS

No.		Page
1	Station 170 Body Bulkhead from Phase I	3
2	Conventionally Fabricated Station 170 Bulkhead Costs Updated Baseline Component	20
3	Finite Element Computer Model of CAST Bulkhead and Transition Structure	24
4	CAST -- Finite Element Computer Model	25
5	CAST -- Finite Element Computer Model	26
6	CAST -- Finite Element Computer Model	27
7	CAST -- Finite Element Computer Model	28
8	CAST -- Finite Element Computer Model	29
9	CAST -- Finite Element Computer Model	30
10	CAST -- Finite Element Computer Model	31
11	CAST -- Finite Element Computer Model	32
12	CAST -- Finite Element Computer Model	33
13	CAST -- Finite Element Computer Model	34
14	CAST -- Finite Element Computer Model Applied Loads . . .	35
15	CAST Bulkhead Critical Lugs at BL 28	36
16	CAST Bulkhead Web Gages and Stresses	37
17	CAST Bulkhead Web (t = 0.1)	38
18	CAST Bulkhead Web (t = 0.14)	39
19	Web Ultimate Shear Stress (Shear Resistant Web Design) . .	40
20	Shear Resistant Web Design	41

ILLUSTRATIONS (Continued)

No.		Page
21	CAST Bulkhead Critical Stiffener BL 28	42
22	Compression Crippling Curves	43
23	CAST Bulkhead Critical Stiffener BL 28	44
24	CAST Bulkhead Critical Stiffener BL 28	45
25	CAST Bulkhead Critical Stiffener BL 28	46
26	CAST Bulkhead Critical Stiffener BL 28	47
27	CAST Bulkhead Critical Stiffener BL 28	48
28	Horizontal Beam at WL 150	49
29	Horizontal Beam at WL 150	50
30	Horizontal Beam at WL 150	51
31	CAST -- Bulkhead Perimeter Chord	52
32	CAST -- Bulkhead Perimeter Chord	53
33	CAST -- Bulkhead Perimeter Chord	54
34	Torque Box at WL 105 L.G. Door Actuator Support	55
35	Torque Box at WL 105 L.G. Door Actuator Support	56
36	Lug Back-up Structure for Lug at BL 8.7	57
37	Damage Tolerance Critical Control Point Locations	58
38	Load Attachment Point A Initial Flaw Location	60
39	Shear Web Initial Flaw Location	61
40	A357 Aluminum Crack Growth Rate Data	62

ILLUSTRATIONS (Continued)

No.		Page
41	A357 Crack Growth Rate Data	72
42	A357 S-N Data for Smooth and Open Hole Specimens	79
43	Detail Design S-N Curves for Smooth Fatigue Specimens . .	80
44	A357 Detail Design S-N Curves for Open Hole Specimens . .	81
45	Station 170 CAST Bulkhead Costs	89

TABLES

No.		Page
1	K_{IC} Plane Strain Fracture Toughness Data	64
2	K_C Plane Stress Fracture Toughness Data	65
3	Flaw Growth Summary for Bulkhead Details	68
4	Material Properties Sensitivity Studies	73
5	Mission Mix Make-up	75
6	Aircraft Usage Sensitivity Studies	75
7	Initial Flaw Assumption Sensitivity Tests	77
8	Load Attachment Point A -- Relative Damage	84
9	Shear Web -- Relative Damage	85
10	Equivalent Initial Flaw Sizes for Types of Defects and X-ray Grades	94

SECTION I

INTRODUCTION

The purpose of the CAST program is to demonstrate that aluminum castings can be used for primary aircraft structural components. The program goal is to achieve the above with no weight penalty and with a minimum of 30% cost savings. The baseline component selected to demonstrate structural casting capability is the YC-14 body bulkhead at body station 170. This is the body nose bulkhead which provides forward support for the nose landing gear and nose gear door, carries cabin pressure on upper segment, and provides support for the nose radome.

The Phase III objective is to complete and release a detail design of the cast bulkhead and the machined bulkhead assembly that meets or exceeds the CAST program goals.

The detail design phase (Phase III) consists of: production drawing preparation to include design layouts for review, analysis, and completion of final production drawings; strength and stability analysis; fatigue and damage tolerance analysis; effects of defects analysis; detail design weight analysis; preparation of detailed projected cost estimates; final review, approval, and release of the production detail design bulkhead; an update of the baseline component data originally released in Phase I; and an on-site review covering Phase III activity.

The detail design of the transition structure and test fixtures will be prepared and released in Phase V, "Structural Test and Evaluation."

This report summarizes the work completed during Phase III.

SECTION II

DETAIL DESIGN

The Phase III Detail Design efforts continued on from Phase I Preliminary Design. The detail design of the production cast bulkhead was based on the final cast bulkhead concept and the preliminary design criteria established in Phase I. Efforts in this phase were on detail drawing completion, analysis, and release to manufacturing, plus an update of the baseline component data.

1. DESIGN LAYOUT

The first design layout of the body station 170 cast bulkhead was an update of the final approved concept from Phase I (fig. 1). Design features of this concept included the following.

- o A close physical match to the existing bulkhead structure, especially in the areas of interface with adjacent structure. This was to provide continuity of existing load paths and required no revision to the adjacent structure.
- o The single casting replaced all parts of the original baseline component plus the crosswise slanted beam at WL 150.
- o Machining of casting is required only for close tolerance contour at skin IML and at nose gear fitting interface locations.
- o Bulkhead web of minimum castable thickness and with the upper pressurized section made in a corrugated form replacing the original stiffened web. A transition section to the lower stiffened web segment is located between WL's 124.6 and 130.

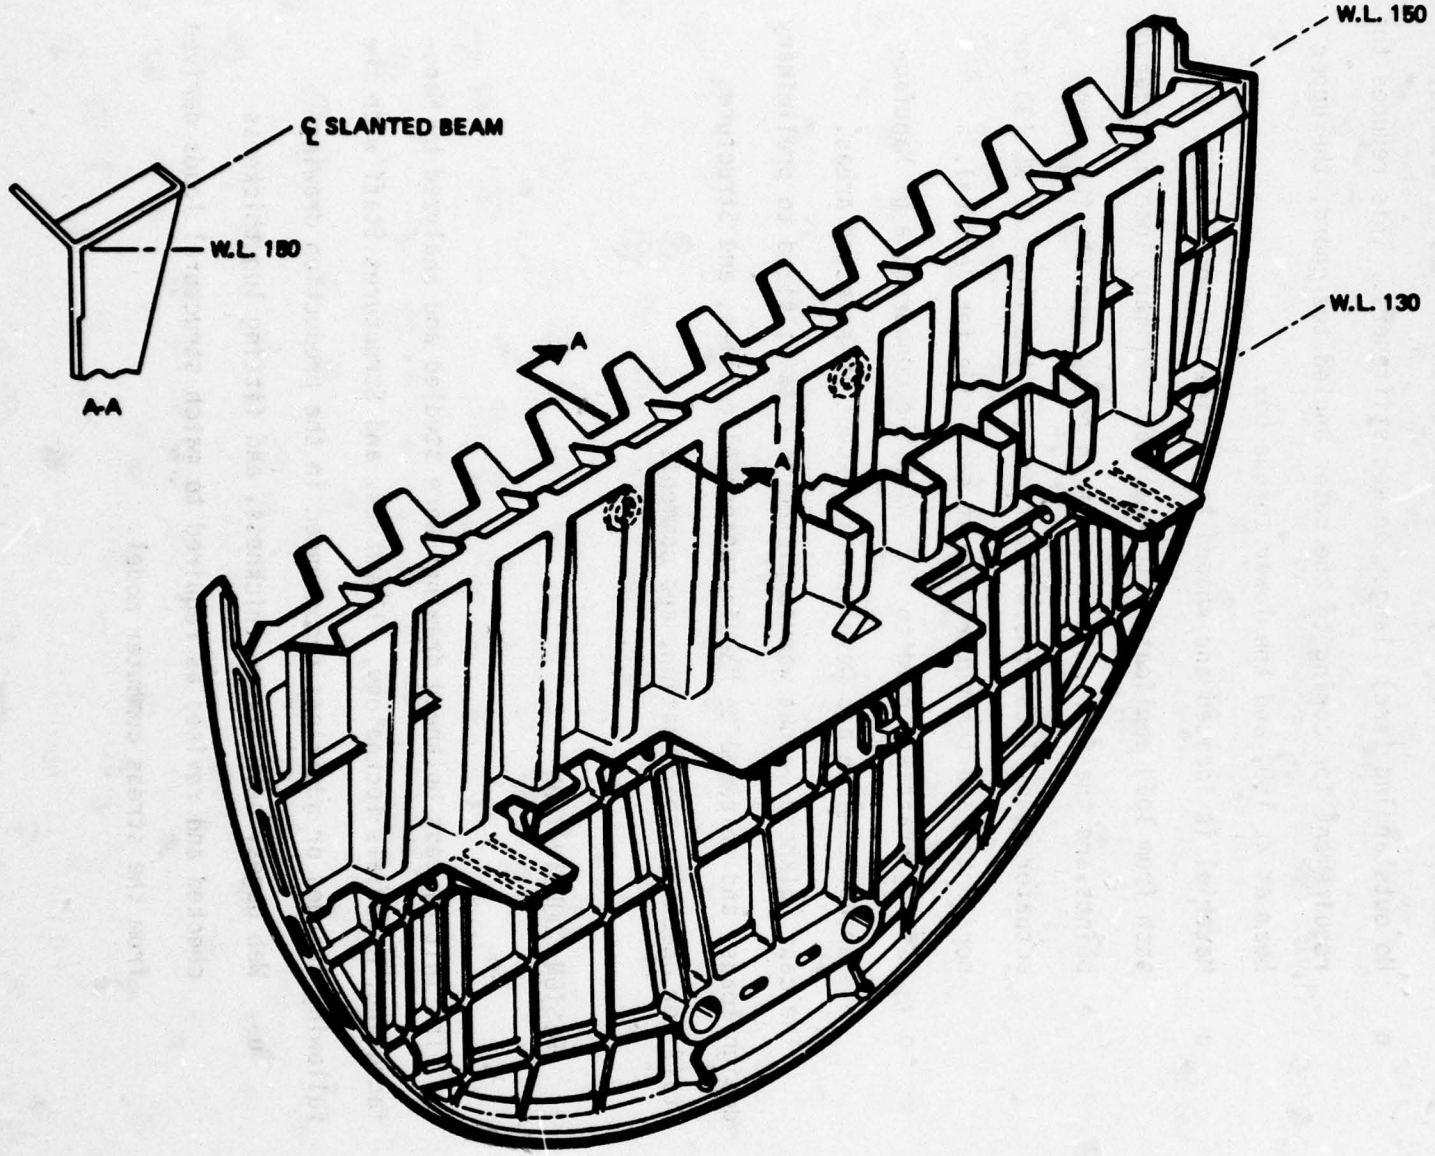

Figure 1 . Station 170 Body Bulkhead From Phase I

- o Below WL 124.6, the web stiffeners extend both fore and aft of the web. The reduced height of the stiffeners from the web provides better castability and reduced amount of draft material.
- o No outstanding (zee) flanges on web stiffeners. This reduces the requirement for coring to the outer angled tee chord, the upper beam at WL 150, and the lower torque box.
- o Material is located and shaped to provide the most direct load path from load application to reaction. Primary load application points are the four nose gear attach points and the two door actuator pivot locations. Reactions are the floor at WL 130 for horizontal and the outer skin at each side for vertical.
- o Casting draft was held to 1/2° with the concurrence of Manufacturing Research and Development, except in selected areas.

The cast bulkhead layout was completed in detail, sized to preliminary design loads, and released to Manufacturing, Allowables, and Structures Staff for checking, coordination, and comments.

2. DESIGN COORDINATION

The initial cast bulkhead drawings were studied and analyzed by Manufacturing, Materials Technology, Allowables, and Structures Staff with the following changes or additions recommended in the production drawing.

- o Web gages, beam flange thickness, and fitting lug thickness checked and revised as required to match structural loads derived from the stress computer model.

- o Added integral cast-on test coupons for mechanical property testing. Located preproduction test coupons to be excised and tested for mechanical properties.
- o The chord casting configuration was revised to remove the step in the parting plane around the periphery of the bulkhead. This reduced cost of the pattern with no increase in machining cost.
- o A cross beam extending outboard and upward from the lower boss for the door actuator pivot to the outer chord was revised to be horizontal. This beam would have crossed from one mold flask to another at a very flat angle, requiring extremely close tolerance in mold assembly. The revision located the beam entirely within one flask.
- o Recesses were added in the large boss at approximately RBL 8.7 and WL 120. These were added for reduction of casting thickness in an area of low stress.

3. DRAWING RELEASE

After completion of drawing revisions resulting from design coordination, the drawings were rechecked and approved by Stress, Design, and Project. Copies of the drawing were then released to Manufacturing organizations, Structures Test, and Structures Staff groups including Stress, Fatigue, Weights, and Allowables.

4. PRODUCTION DRAWINGS

The production bulkhead casting drawing, 162-00017, is a four-sheet drawing on mylar with a half-size rear view and full-size section views.

The production bulkhead assembly drawing, 162-00018, is a four-sheet drawing made from "brown line" reproducible copies of the bulkhead casting drawing. This drawing deletes the basic casting dimensioning and adds machining dimensions, bushings, inspection requirements, and finishes.

a. Bulkhead Casting

Drawing 162-00017 Sheets 1 through 4 were reduced to document size and are included for reference only (pages 7 through 10).

b. Bulkhead Assembly

Drawing 162-00018 Sheets 1 through 4 were reduced to document size and are included for reference only (pages 11 through 14.

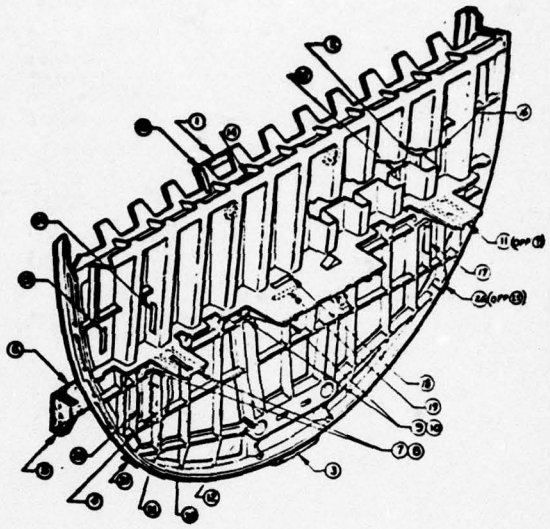

TABLE 1

SPECIMEN	DAS (MAX) (.XXX in)	ASTM-B CROWN CONFIG
1		FLAT
2		FLAT
3		ROUND
4		FLAT
5		ROUND
6		FLAT
7		ROUND
8		〃
9		〃
10		〃
11		ROUND
12		FLAT
13		〃
14		
15		
16		
17		
18		
19		
20		
21		
22		
23		
24		
25		
26		
27		
28		
29		
30		
31		
32		
33		
34		
35		
36		
37		
38		
39		
40		
41		
42		
43		
44		
45		
46		
47		
48		
49		
50		
51		
52		
53		
54		
55		
56		
57		
58		
59		
60		
61		
62		
63		
64		
65		
66		
67		
68		
69		
70		
71		
72		
73		
74		
75		
76		
77		
78		
79		
80		
81		
82		
83		
84		
85		
86		
87		
88		
89		
90		
91		
92		
93		
94		
95		
96		
97		
98		
99		
100		
101		
102		
103		
104		
105		
106		
107		
108		
109		
110		
111		
112		
113		
114		
115		
116		
117		
118		
119		
120		
121		
122		
123		
124		
125		
126		
127		
128		
129		
130		
131		
132		
133		
134		
135		
136		
137		
138		
139		
140		
141		
142		
143		
144		
145		
146		
147		
148		
149		
150		
151		
152		
153		
154		
155		
156		
157		
158		
159		
160		
161		
162		
163		
164		
165		
166		
167		
168		
169		
170		
171		
172		
173		
174		
175		
176		
177		
178		
179		
180		
181		
182		
183		
184		
185		
186		
187		
188		
189		
190		
191		
192		
193		
194		
195		
196		
197		
198		
199		
200		
201		
202		
203		
204		
205		
206		
207		
208		
209		
210		
211		
212		
213		
214		
215		
216		
217		
218		
219		
220		
221		
222		
223		
224		
225		
226		
227		
228		
229		
230		
231		
232		
233		
234		
235		
236		
237		
238		
239		
240		
241		
242		
243		
244		
245		
246		
247		
248		
249		
250		
251		
252		
253		
254		
255		
256		
257		
258		
259		
260		
261		
262		
263		
264		
265		
266		
267		
268		
269		
270		
271		
272		
273		
274		
275		
276		
277		
278		
279		
280		
281		
282		
283		
284		
285		
286		
287		
288		
289		
290		
291		
292		
293		
294		
295		
296		
297		
298		
299		
300		
301		
302		
303		
304		
305		
306		
307		
308		
309		
310		
311		
312		
313		
314		
315		
316		
317		
318		
319		
320		
321		
322		
323		
324		
325		
326		
327		
328		
329		
330		
331		
332		
333		
334		
335		
336		
337		
338		
339		
340		
341		
342		
343		
344		
345		
346		
347		
348		
349		
350		
351		
352		
353		
354		
355		
356		
357		
358		
359		
360		
361		
362		
363		
364		
365		
366		
367		
368		
369		
370		
371		
372		
373		
374		
375		
376		
377		
378		
379		
380		
381		
382		
383		
384		
385		
386		
387		
388		
389		
390		
391		
392		
393		
394		
395		
396		
397		
398		
399		
400		
401		
402		
403		
404		
405		
406		
407		
408		
409		
410		
411		
412		
413		
414		
415		
416		
417		
418		
419		
420		
421		
422		
423		
424		
425		
426		
427		
428		
429		
430		
431		
432		
433		
434		
435		
436		
437		
438		
439		
440		
441		
442		
443		
444		
445		
446		
447		
448		
449		
450		
451		
452		
453		
454		
455		
456		
457		
458		
459		
460		
461		
462		
463		
464		
465		
466		
467		
468		
469		
470		
471		
472		
473		
474		
475		
476		
477		
478		
479		
480		
481		
482		
483		
484		
485		
486		
487		
488		
489		
490		
491		
492		
493		
494		
495		
496		
497		
498		
499		
500		
501		
502		
503		
504		
505		
506		
507		
508		
509		
510		
511		
512		
513		
514		
515		
516		
517		
518		
519		
520		
521		
522		
523		
524		
525		
526		
527		
528		
529		
530		
531		
532		
533		
534		
535		
536		
537		
538		
539		
540		
541		
542		
543		
544		
545		
546		
547		
548		
549		
550		
551		
552		
553		
554		
555		
556		
557		
558		
559		
560		
561		
562		
563		
564		
565		
566		
567		
568		
569		
570		
571		
572		
573		
574		
575		
576		
577		
578		
579		
580		
581		
582		
583		
584		
585		
586		
587		
588		
589		
590		
591		
592		
593		
594		
595		
596		
597		
598		
599		
600		
601		
602		
603		
604		
605		
606		
607		
608		
609		
610		
611		
612		
613		
614		
615		
616		
617		
618		
619		
620		
621		
622		
623		
624		
625		
626		
627		
628		
629		
630		
631		
632		
633		
634		
635		
636		
637		
638		
639		
640		
641		
642		
643		
644		
645		
646		
647		
648		
649		
650		
651		
652		
653		
654		
655		
656		
657		
658		
659		
660		
661		
662		
663		
664		
665		
666		
667		
668		
669		
670		
671		
672		
673		
674		
675		
676		
677		
678		
679		
680		
681		
682		
683		
684		
685		
686		
687		
688		
689		
690		
691		
692		
693		
694		
695		
696		
697		
698		
699		
700		
701		
702		
703		
704		
705		
706		
707		
708		
709		
710		
711		
712		
713		
714		
715		
716		
717		
718		
719		
720		
721		
722		
723		
724		
725		
726		
727		
728		
729		
730		
731		
732		
733		
734		
735		
736		
737		
738		
739		
740		
741		
742		
743		
744		
745		
746		
747		
748		
749		
750		
751		
752		
753		
754		
755		
756		
757		
758		
759		
760		
761		
762		
763		
764		
765		
766		
767		
768		
769		
770		
771		
772		
773		
774		
775		
776		
777		
778		
779		
780		
781		
782		
783		
784		
785		
786		
787		
788		
789		
790		
791		
792		
793		
794		
795		
796		
797		
798		
799		
800		
801		
802		
803		
804		
805		
806		
807		
808		
809		
810		
811		
812		
813		
814		
815		
816		
817		
818		
819		
820		
821		
822		
823		
824		
825		
826		
827		
828		
829		
830		
831		
832		
833		
834		
835		
836		
837		
838		
839		
840		
841		
842		
843		
844		
845		
846		
847		
848		
849		
850		
851		
852		
853		
854		
855		
856		
857		
858		
859		
860		
861		
862		
863		
864		
865		
866		
867		
868		
869		
870		
871		
872		
873		
874		
875		
876		
877		
878		
879		
880		
881		
882		
883		
884		
885		
886		
887		
888		
889		
890		
891		
892		
893		
894		
895		
896		
897		
898		
899		
900		
901		
902		
903		
904		
905		
906		
907		
908		
909		
910		
911		
912		
913		
914		
915		
916		
917		
918		
919		
920		
921		
922		
923		
924		
925		
926		
927		
928		
929		
930		
931		
932		
933		
934		
935		
936		
937		
938		
939		
940		
941		
942		
943		
944		
945		
946		
947		
948		
949		
950		
951		
952		
953		
954		
955		
956		
957		
958		
959		
960		
961		
962		
963		
964		
965		
966		
967		
968		
969		
970		
971		
972		
973		
974		
975		
976		
977		
978		
979		
980		
981		
982		
983		
984		
985		
986		
987		
988		
989		
990		
991		
992		
993		
994		
995		
996		
997		
998		
999		
1000		

MECHANICAL PROPERTY TEST COUPON INFORMATION

① THRU ⑥ - INTEGRAL CAST-ON COUPONS

⑦ THRU ⑫, ⑪ OPP ⑫ & ⑬ LUG SPECIMENS — PREPRODUCTION TEST

⑭ & ⑮ SLANTED BEAM SPECIMENS — EXCISED COUPONS

⑯ THRU ㉓ & ㉔ (OPP ㉓) WEB, FLANGE OR CHORD SPECIMENS

MEASURE DENDRITE ARM SPACING (DAS) PER MIL-Y-XXXX (CAST) ACCEPTABLE DAS VALUES ARE LISTED IN TABLE 1

TEST ALL TENSILE SPECIMENS PER MIL-A-XXXX (CAST).

ALL TENSILE COUPONS SHALL BE PERMANENTLY IDENTIFIED BY CASTING ℄ LOCATION.

ALL EXCESS PORTIONS OF A CASTING WHICH ARE REMOVED DURING THE EXCISION OF TENSILE COUPONS MUST BE PERMANENTLY MARKED FOR IDENTIFICATION.

SEE DRAWING (SHT 2, 3 & 4) FOR DETAILED LOCATION OF SPECIMENS.

-1	162-00018	CAST PROGRAM	TEST ONLY	
REVISION	SHEET NUMBER		EFFECTIVITY APPLICATION	

NOTES

REV STATUS

LTR	STATUS
2	A
3	A
4	A

REVISIONS

ZONE	LTR	DESCRIPTION	DATE	APPROVED

(D) DATUM TARGET POINT DIMENSION. GENL DWG TOL DOES NOT APPLY

(D) HORIZONTAL DIMENSION TO DATUM PLANE C (R.B.L. .291 REF)

(C) STEP RESULTING FROM CASTING DRAFT

(B) CLASS 1, GRADE B IN CRITICALLY STRESSED AREAS. GRADE C ELSEWHERE PER MIL-A-XXXX. INSPECT PER MIL-A-XXXX SECTION 4. CRITICALLY STRESSED AREAS DEFINED ON DRAWING AS SHOWN: C____.

(E) RAISED .25 LETTERS & NUMBERS (RUBBER STAMP OPTIONAL)

2 DIMENSIONS & TOLERANCES EXCEPT AS NOTED

EDGE RADII	.03 ± .03
FILLET RADII	.25 ± .06
CORNER RADII	.06 ± .06
DRAFT ANGLE	½° MAX

SEE DIM & TOL BLOCK, ZN A-2
BREAK ALL SHARP EDGES .02 MIN

(F) HEAT TREAT TG PER MIL-A-XXXX, 3.1.8, 3.2.6 & 3.3.5

(G) WELD CORRECTION OF DEFECTS DETECTED PRIOR TO MACHINING IS ALLOWED
PER MIL-W-XXXX (CAST)
HEAT TREAT CORRECTED CASTING PER (F)
INSPECT CORRECTED CASTING PER (E)

MIL-W-XXXX (CAST)	PROCESS SPEC
MIL-Y-XXXX (CAST)	PROCESS SPEC

QTY REQD	FIND NUMBER	PART OR IDENTIFYING NUMBER	NOMENCLATURE OR DESCRIPTION	ZONE	MATERIAL AND SPECIFICATION	CODE IDENT NO	HT TR	FINISH	PT SPEC	REV LTR
	-1	BULKHEAD CASTING	A4-2		A357 ALUMINUM PER MIL-A-XXXX (CAST)		(F)	F2.10	(G)	

PART'S LIST

DIMENSIONS & TOLERANCES PER ANSI Y14.5

UNLESS OTHERWISE SPECIFIED
DIMENSIONS ARE IN INCHES
TOLERANCES: ANGLES ± ½°
DECIMALS .XX ± .03
DECIMALS .XXX ± .010
RIVET & BOLT EDGE MARGINS IN SHEET METAL GREATER THAN 1 DIA OR 150 % GREATER THAN 2 DIA OR 200 % GREATER
SHEET METAL CORNER RADII: SHT THK 10 OR LESS, RAD 25; SHT THK 12, RAD 50

REVISED & APPROVED

DRAWN Gail 8-2-77
STR-CAL [illegible] 8-2-77
WT & PRICE
CHANGE/ADD NUMBER

CUSTODY NUMBER F33615-76-C-3111
DRAWN P. Gomez 7-1-77
CHK
ENGR [illegible] 7-1-7
ORG QUALITY [illegible] 8-2-7
PROJECT APPROVAL [illegible] 7/14

THE BOEING COMPANY
CORPORATE OFFICES SEATTLE, WASHINGTON 98124

BULKHEAD CASTING
STATION 170
CAST

SIZE J | CODE IDENT NO 81205 | 162-00017
SCALE — | SH 1 OF 4

FASTENER CODES

T ONLY | 1234 | EFFECTIVITY | DWG SH NUMBER | REV LTR

162-00017 11

162-00017 11

7

2

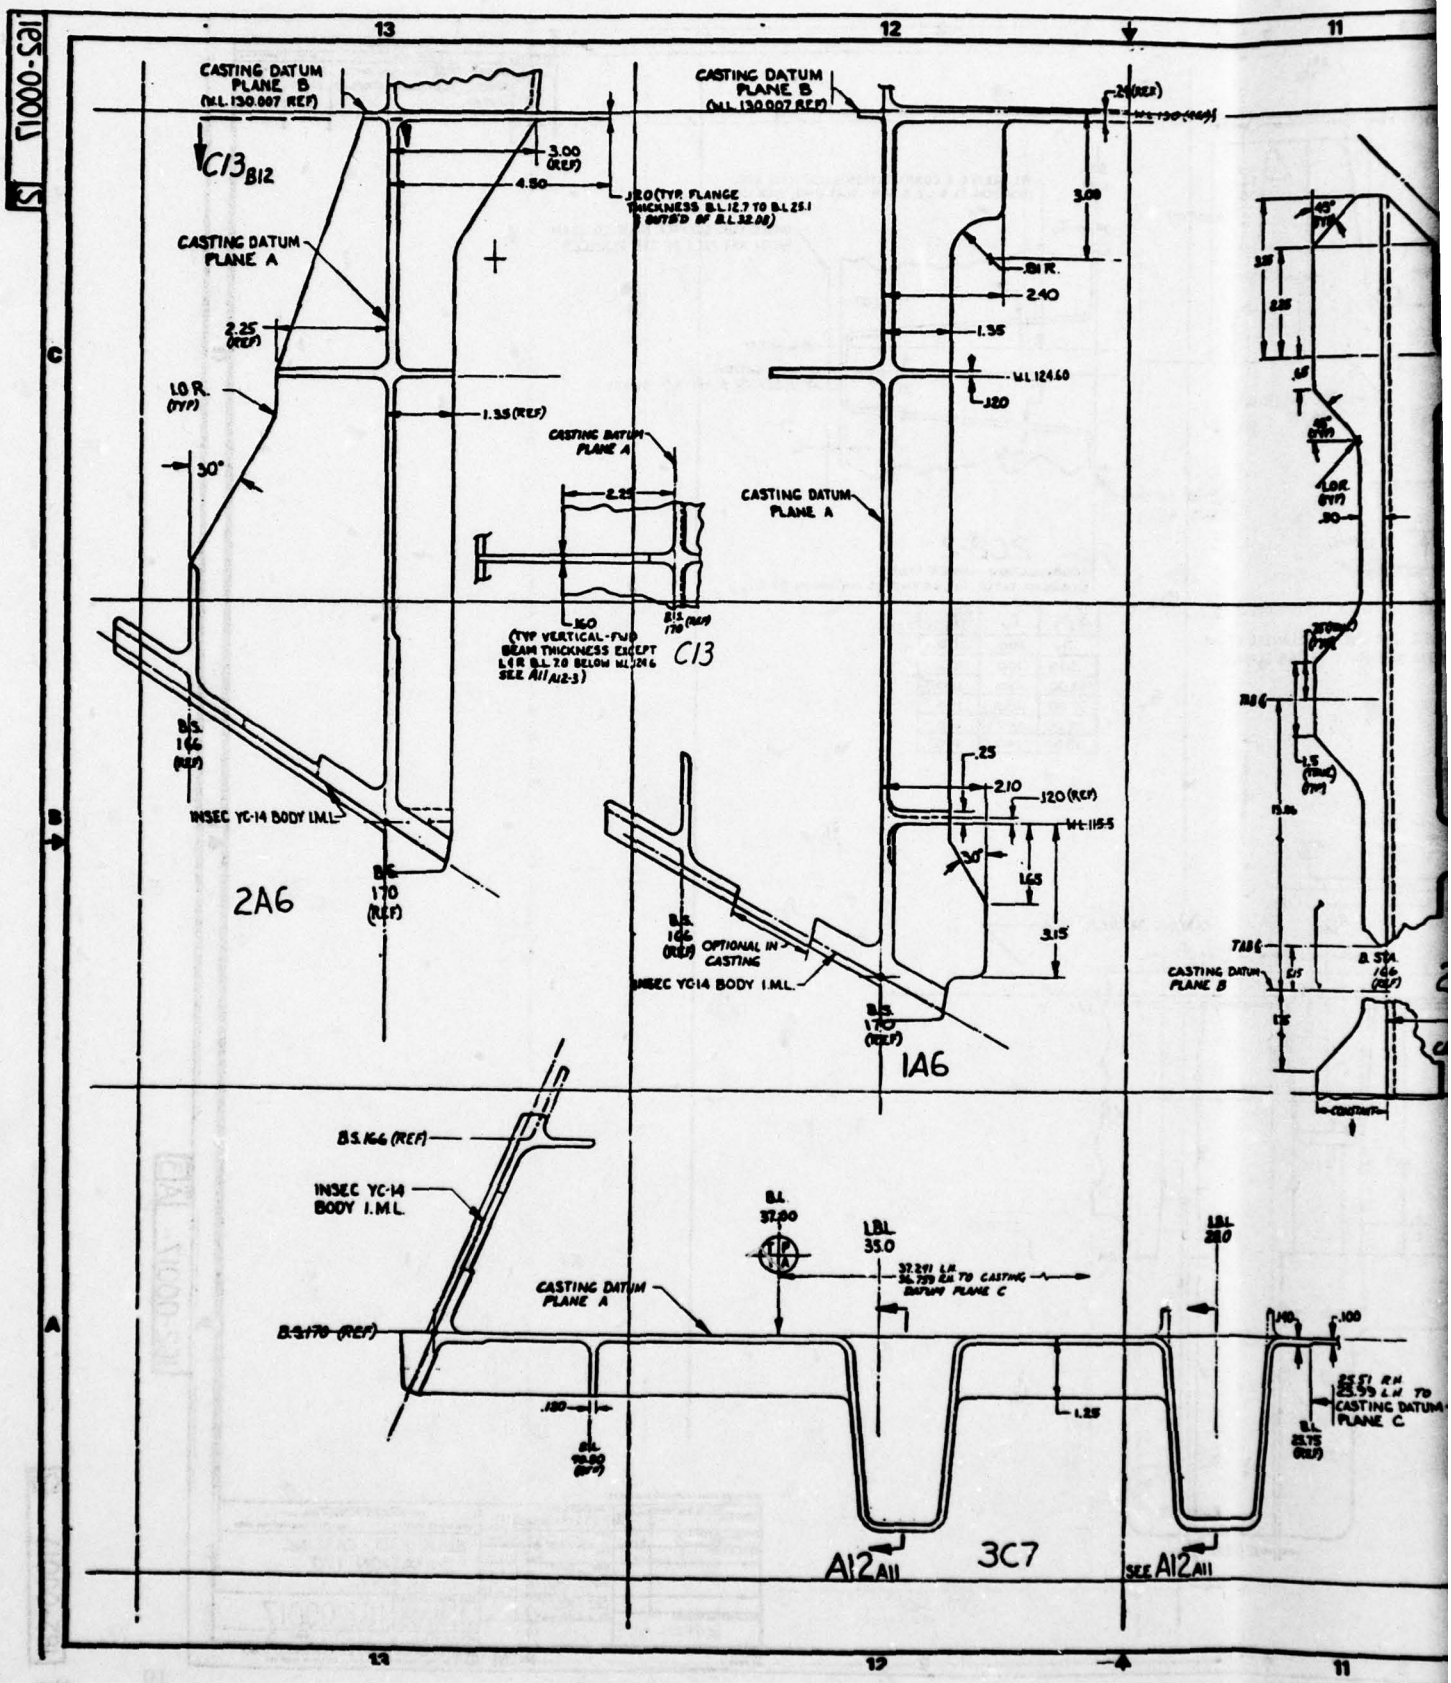
13
12
11
C
B
A
CASTING DATUM PLANE B (W.L. 130.007 REF)
C13 B12
3.00 (REF)
4.50
.120 (TYP FLANGE THICKNESS B.L 12.7 TO B.L 25.1 & OUTBD OF B.L 32.80)
CASTING DATUM PLANE A
2.25 (REF)
1.0 R. (TYP)
1.35 (REF)
30°
.160 (TYP VERTICAL-FWD BEAM THICKNESS EXCEPT L & R B.L 70 BELOW W.L 246 SEE A11 A12-3)
C13
B.S. 166 (REF)
INSEC YC-14 BODY I.M.L.
B.S. 170 (REF)
2A6
CASTING DATUM PLANE B (W.L. 130.007 REF)
2.40 (REF)
3.00
.81 R.
2.40
1.35
W.L 124.60
.120
CASTING DATUM PLANE A
.25
2.10
120 (REF)
W.L 115.5
30°
1.65
3.15
B.S. 166 (REF)
OPTIONAL IN CASTING
INSEC YC14 BODY I.M.L.
B.S. 170 (REF)
1A6
45° TYP
.325
.225
.65
.80 (TYP)
L & R (TYP)
.80
7.86
1.5 (TYP)
(TYP)
15.84
7.86
CASTING DATUM PLANE B
.65
B.S. 166 (REF)
.125
CONSTRUCTION
B.S. 166 (REF)
INSEC YC-14 BODY I.M.L.
B.S. 170 (REF)
.180
B.L. 19.00 (REF)
B.L. 37.80
LBL 35.0
37.291 LH 36.739 RH TO CASTING DATUM PLANE C
CASTING DATUM PLANE A
1.25
LBL 28.0
.140
.100
B.L. 23.75 (REF)
SEE A12 A11 23.99 LH TO CASTING DATUM PLANE C
A12 A11
3C7
SEE A12 A11

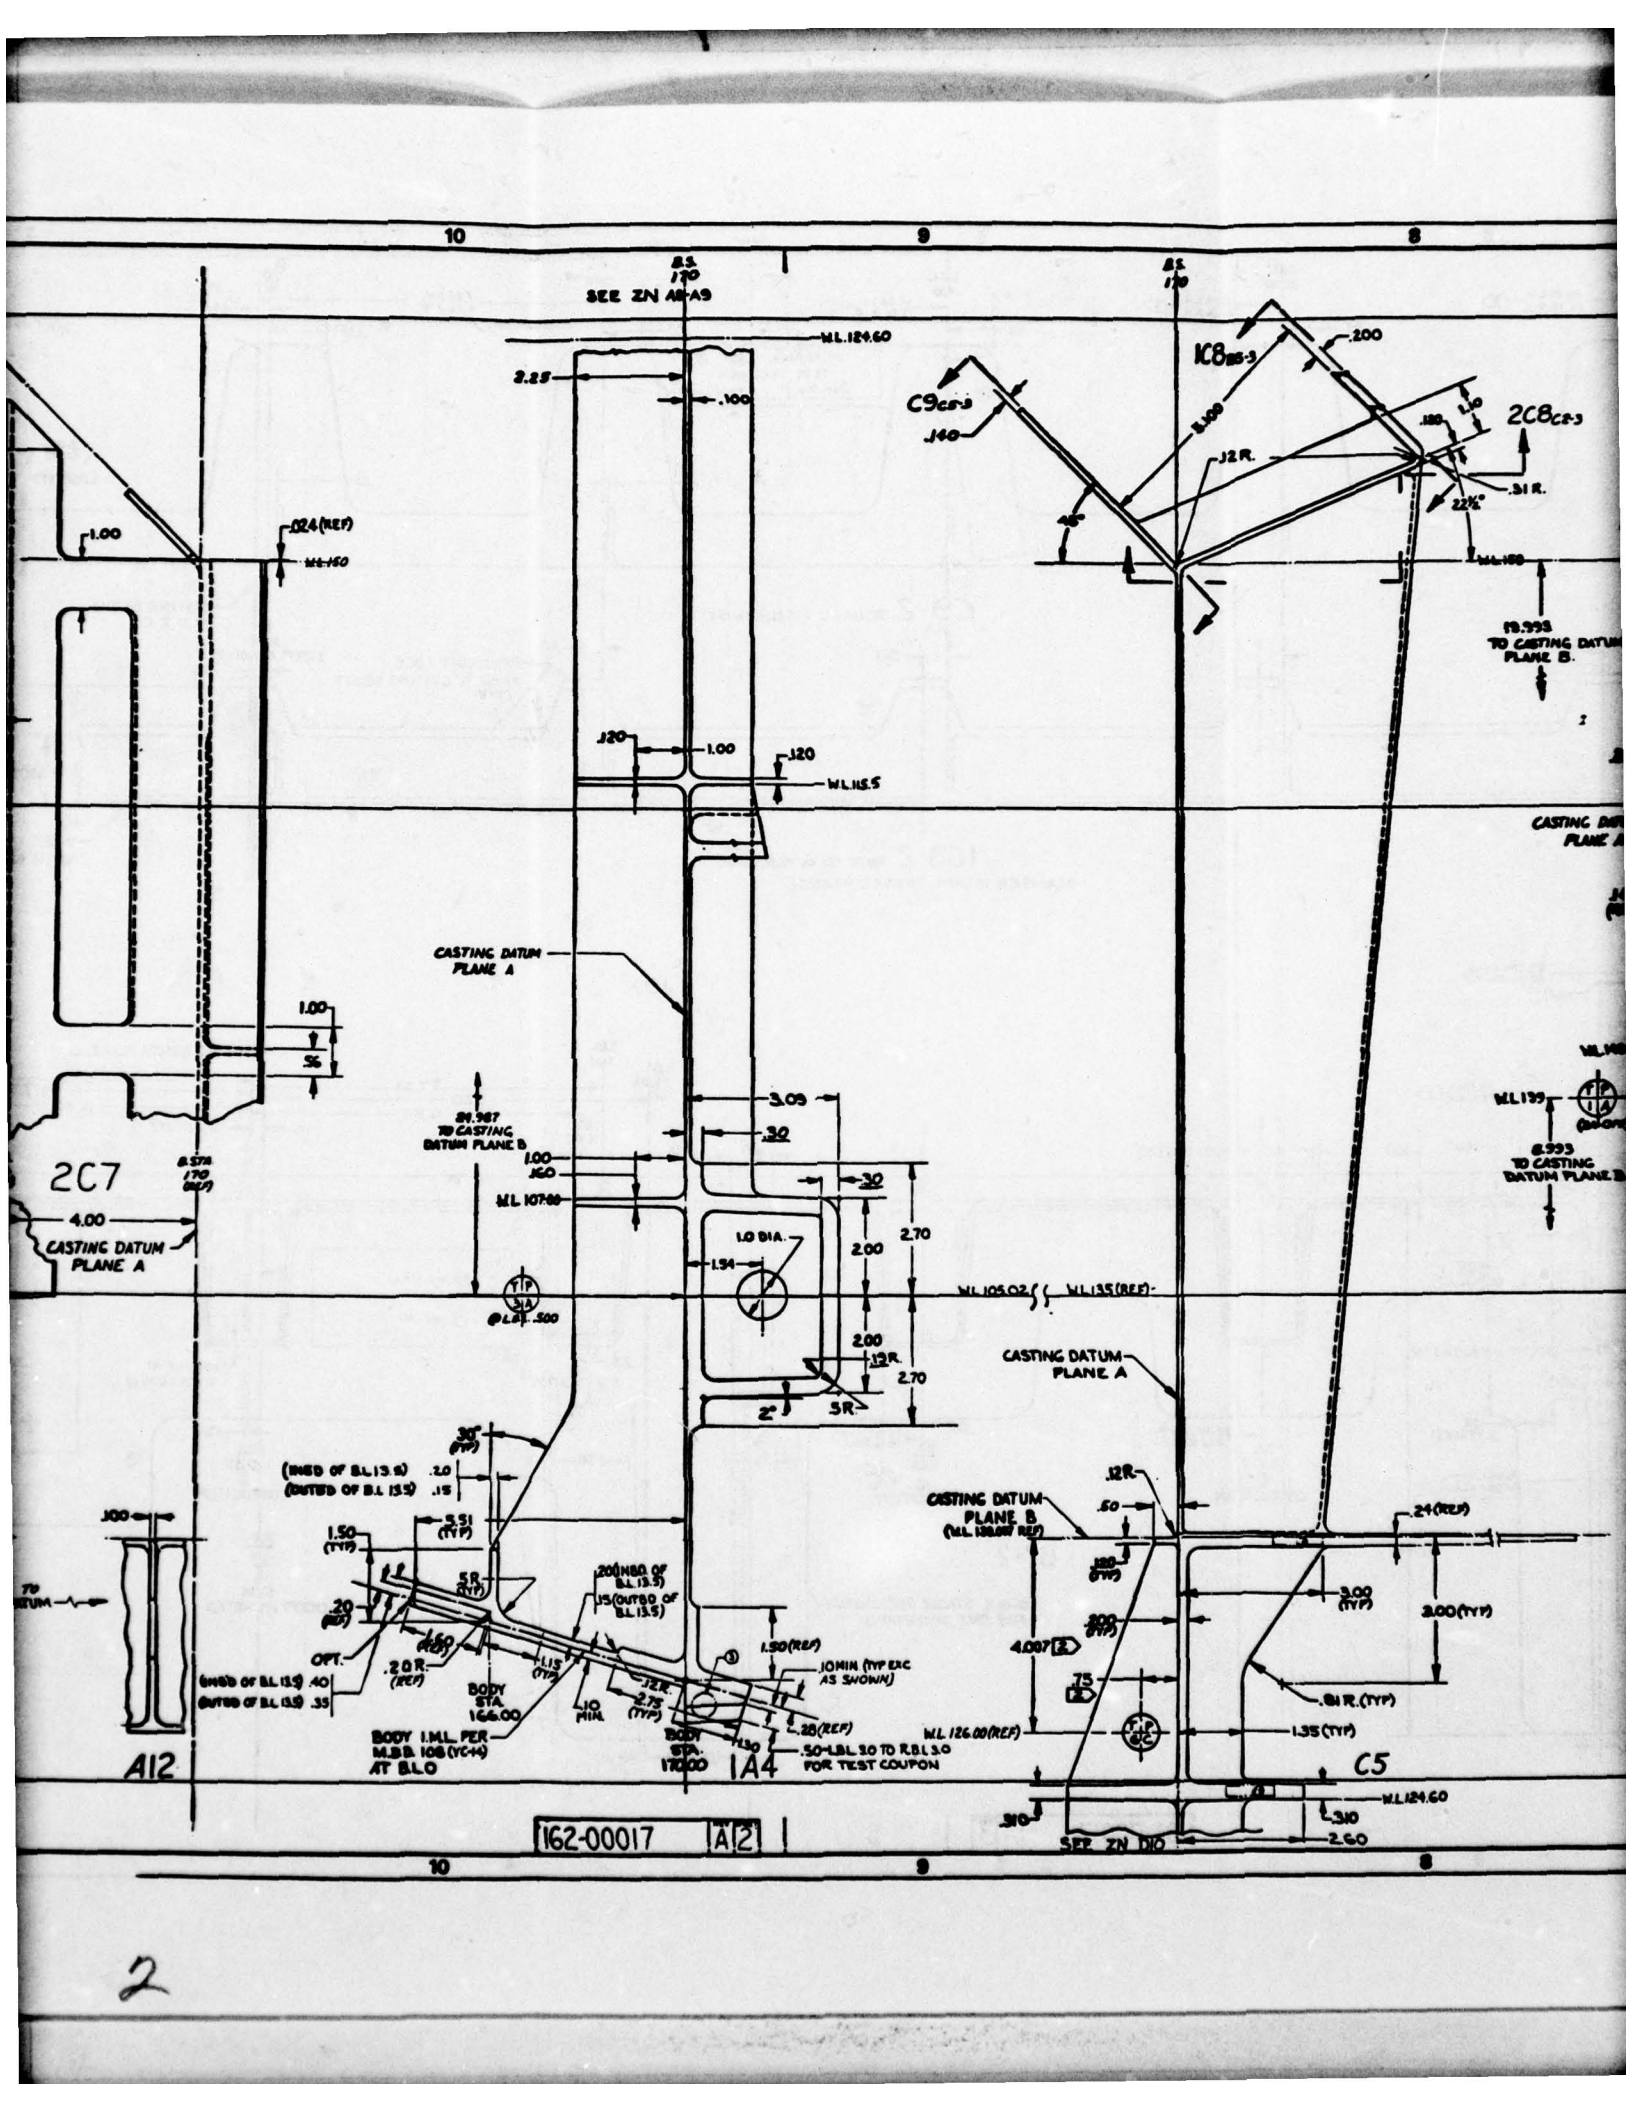
10
9
8
SEE ZN A8-A9
W.L. 124.60
2.25
.100
C9 CF-3
.140
1C8 BS-3
.200
2C8 CF-3
.12 R.
.31 R.
22½°
W.L. 150
1.00
.024 (REF)
19.393
TO CASTING DATUM PLANE B.
.120
1.00
.120
W.L. 115.5
CASTING DATUM PLANE A
1.00
.56
2C7
4.00
CASTING DATUM PLANE A
19.987
TO CASTING DATUM PLANE B
3.09
.30
.30
1.00
.160
W.L. 107.88
1.0 DIA.
1.54
2.00
2.70
2.00
.12 R.
2.70
2°
5 R.
W.L. 105.02
W.L. 135 (REF)
@ L.B.L. .500
CASTING DATUM PLANE A
W.L. 139
6.993
TO CASTING DATUM PLANE B
.12 R.
.50
CASTING DATUM PLANE B
(W.L. 138.007 REF)
.24 (REF)
.120 (TYP)
3.00 (TYP)
3.00 (TYP)
.200 (TYP)
4.007
.75
.81 R. (TYP)
W.L. 126.00 (REF)
1.35 (TYP)
C5
W.L. 124.60
.310
.310
2.60
SEE ZN D10
30° (TYP)
(INSD OF B.L. 13.5) .20
(OUTSD OF B.L. 13.5) .15
.100
1.50 (TYP)
5.51 (TYP)
5 R. (TYP)
.20 (REF)
.20 (REF)
.20 R. (REF)
OPT.
(INSD OF B.L. 13.5) .40
(OUTSD OF B.L. 13.5) .35
BODY STA. 166.00
.115 (TYP)
.10 MIN.
.12 R.
2.75 (TYP)
.20 (INSD OF B.L. 13.5)
.15 (OUTSD OF B.L. 13.5)
1.50 (REF)
.10 MIN (TYP EXC AS SHOWN)
.20 (REF)
.50 L.B.L. 3.0 TO R.B.L. 3.0 FOR TEST COUPON
BODY STA. 170.00
BODY I.M.L. PER M.B.B. 108 (YC-14) AT B.L. 0
A12
A4
162-00017 A2

2

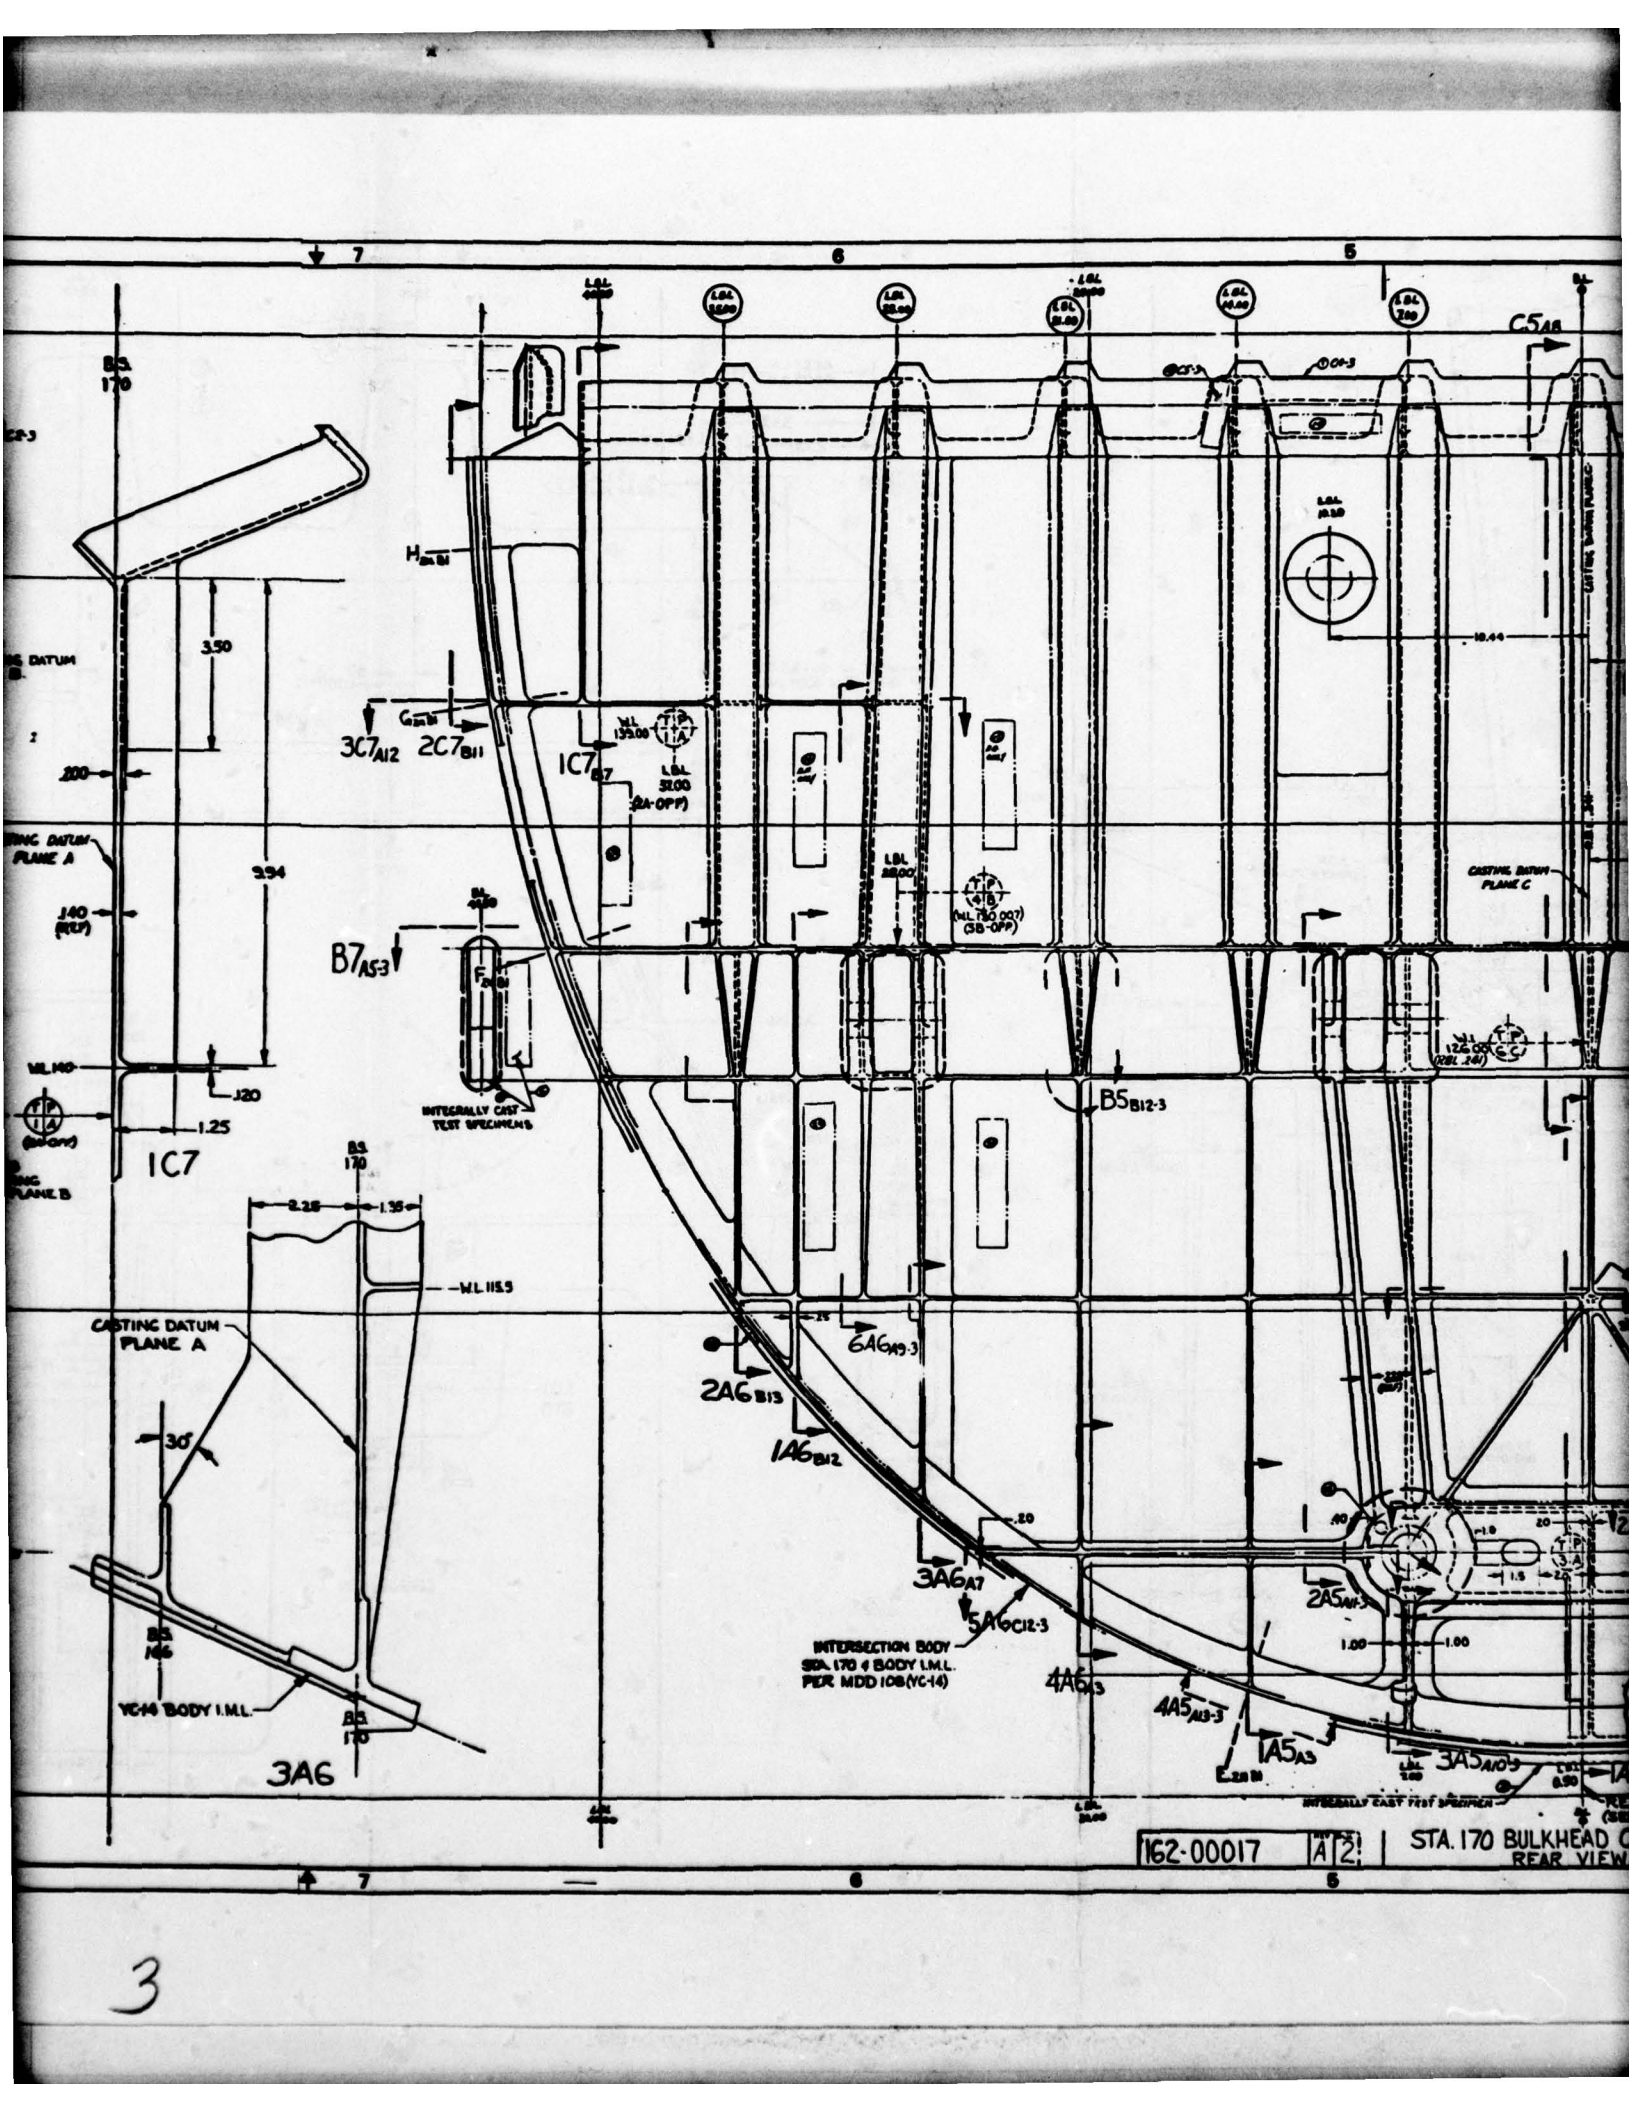
7
6
5
BS 170
3C7 A12
2C7 B11
1C7 B7
B7 A5-3
B5 B12-3
C5 A8
3.50
3.94
.200
.140 (REF)
.320
1.25
1C7
WL 140
INTEGRALLY CAST TEST SPECIMENS
CASTING DATUM PLANE A
CASTING DATUM PLANE B
CASTING DATUM PLANE C
2.28
1.35
WL 115.5
30°
BS 146
BS 170
YC-14 BODY I.M.L.
3A6
6A6 A9-3
2A6 B13
1A6 B12
3A6 A7
5A6 C12-3
INTERSECTION BODY STA. 170 & BODY I.M.L. PER MDD 108 (YC-14)
4A6 A13
4A5 A13-3
1A5 A3
2A5 A11-3
3A5 A10-3
162-00017
A
2
STA. 170 BULKHEAD
REAR VIEW

3

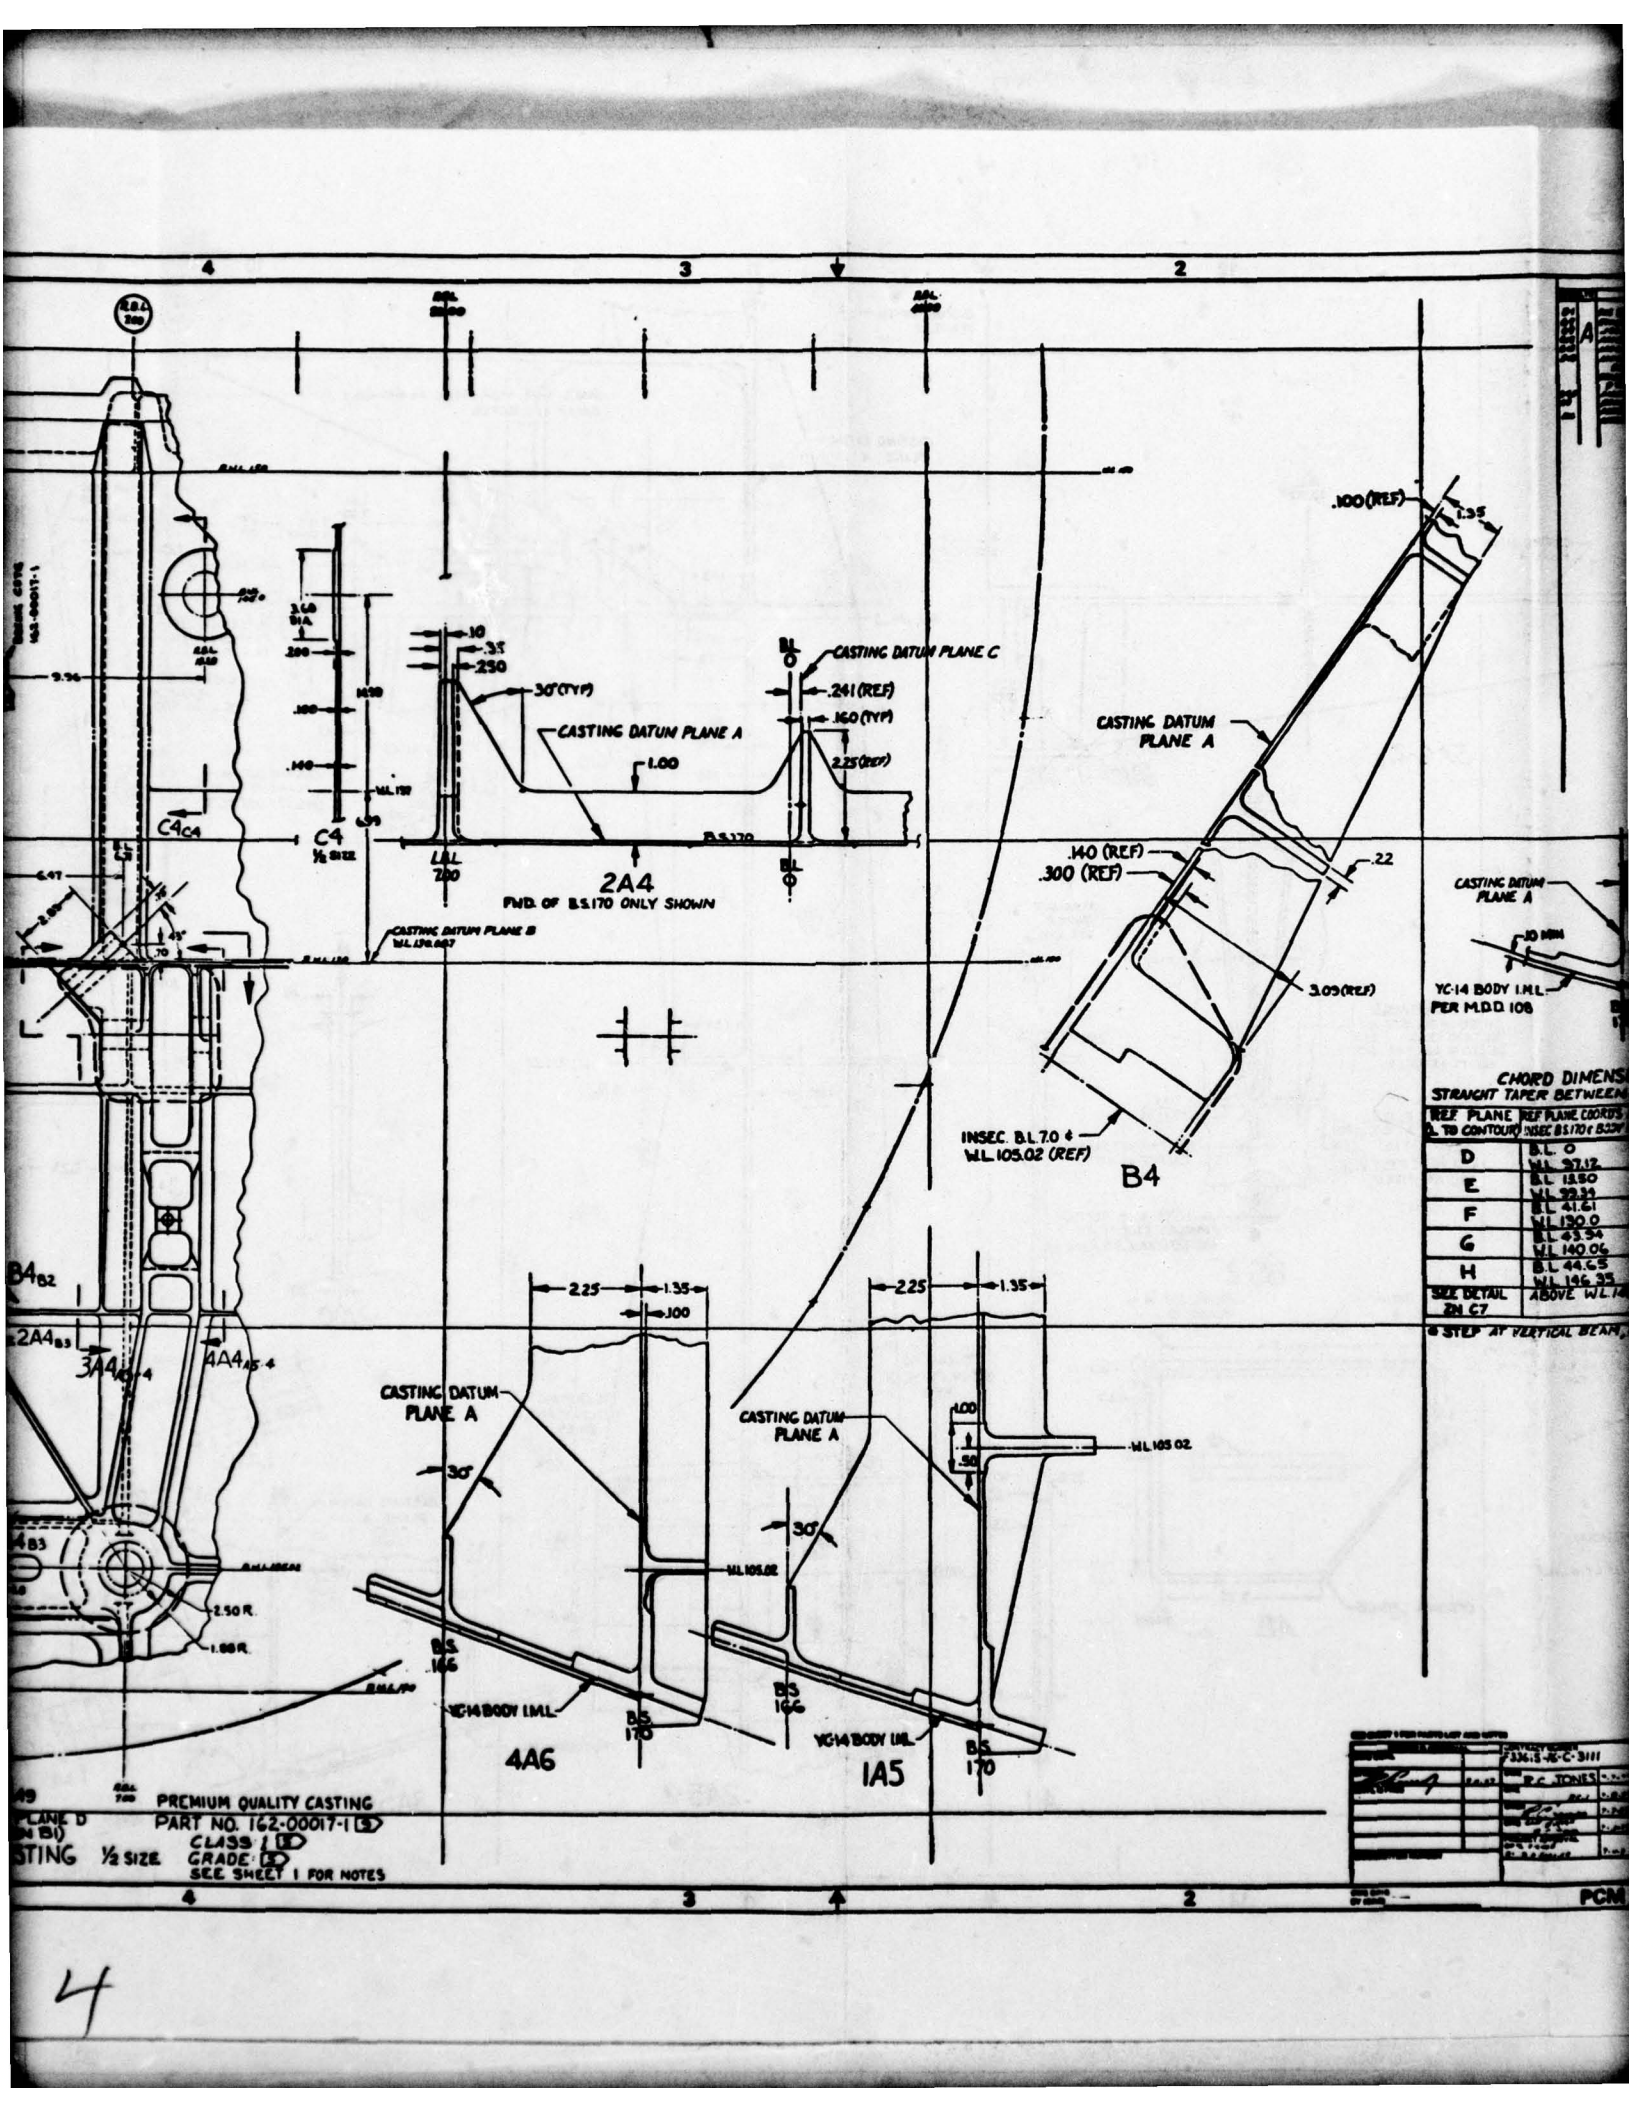
4
3
2
C4
½ SIZE
C4
2A4
FWD. OF B.S.170 ONLY SHOWN
CASTING DATUM PLANE A
CASTING DATUM PLANE C
CASTING DATUM PLANE B
30° (TYP)
.241 (REF)
.160 (TYP)
2.25 (REF)
1.00
.10
.35
2.30
B.S.170
W.L. 130.667
.100 (REF)
1.35
.140 (REF)
.300 (REF)
.22
3.09 (REF)
INSEC. B.L. 7.0 ¢
W.L. 105.02 (REF)
B4
CASTING DATUM PLANE A
10 MIN
YC-14 BODY I.M.L.
PER M.D.D. 108
CHORD DIMENS
STRAIGHT TAPER BETWEEN
REF PLANE ⊥ TO CONTOUR
REF PLANE COORDS INSEC B.S.170 ¢ BODY
D
B.L. 0
W.L. 97.12
E
B.L. 13.50
W.L. 99.39
F
B.L. 41.61
W.L. 130.0
G
B.L. 43.54
W.L. 140.06
H
B.L. 44.65
W.L. 146.35
SEE DETAIL ZN C7
ABOVE W.L. 14
@ STEP AT VERTICAL BEAM
B4 B2
2A4 B3
3A4 B3-4
4A4 B5-4
4 B3
2.50 R.
1.88 R.
2.25
1.35
.100
CASTING DATUM PLANE A
30°
W.L. 105.02
B.S. 166
YC-14 BODY I.M.L.
B.S. 170
4A6
.100
.50
1A5
PREMIUM QUALITY CASTING
PART NO. 162-00017-1
CLASS 1
GRADE
SEE SHEET 1 FOR NOTES
½ SIZE
PCM

4

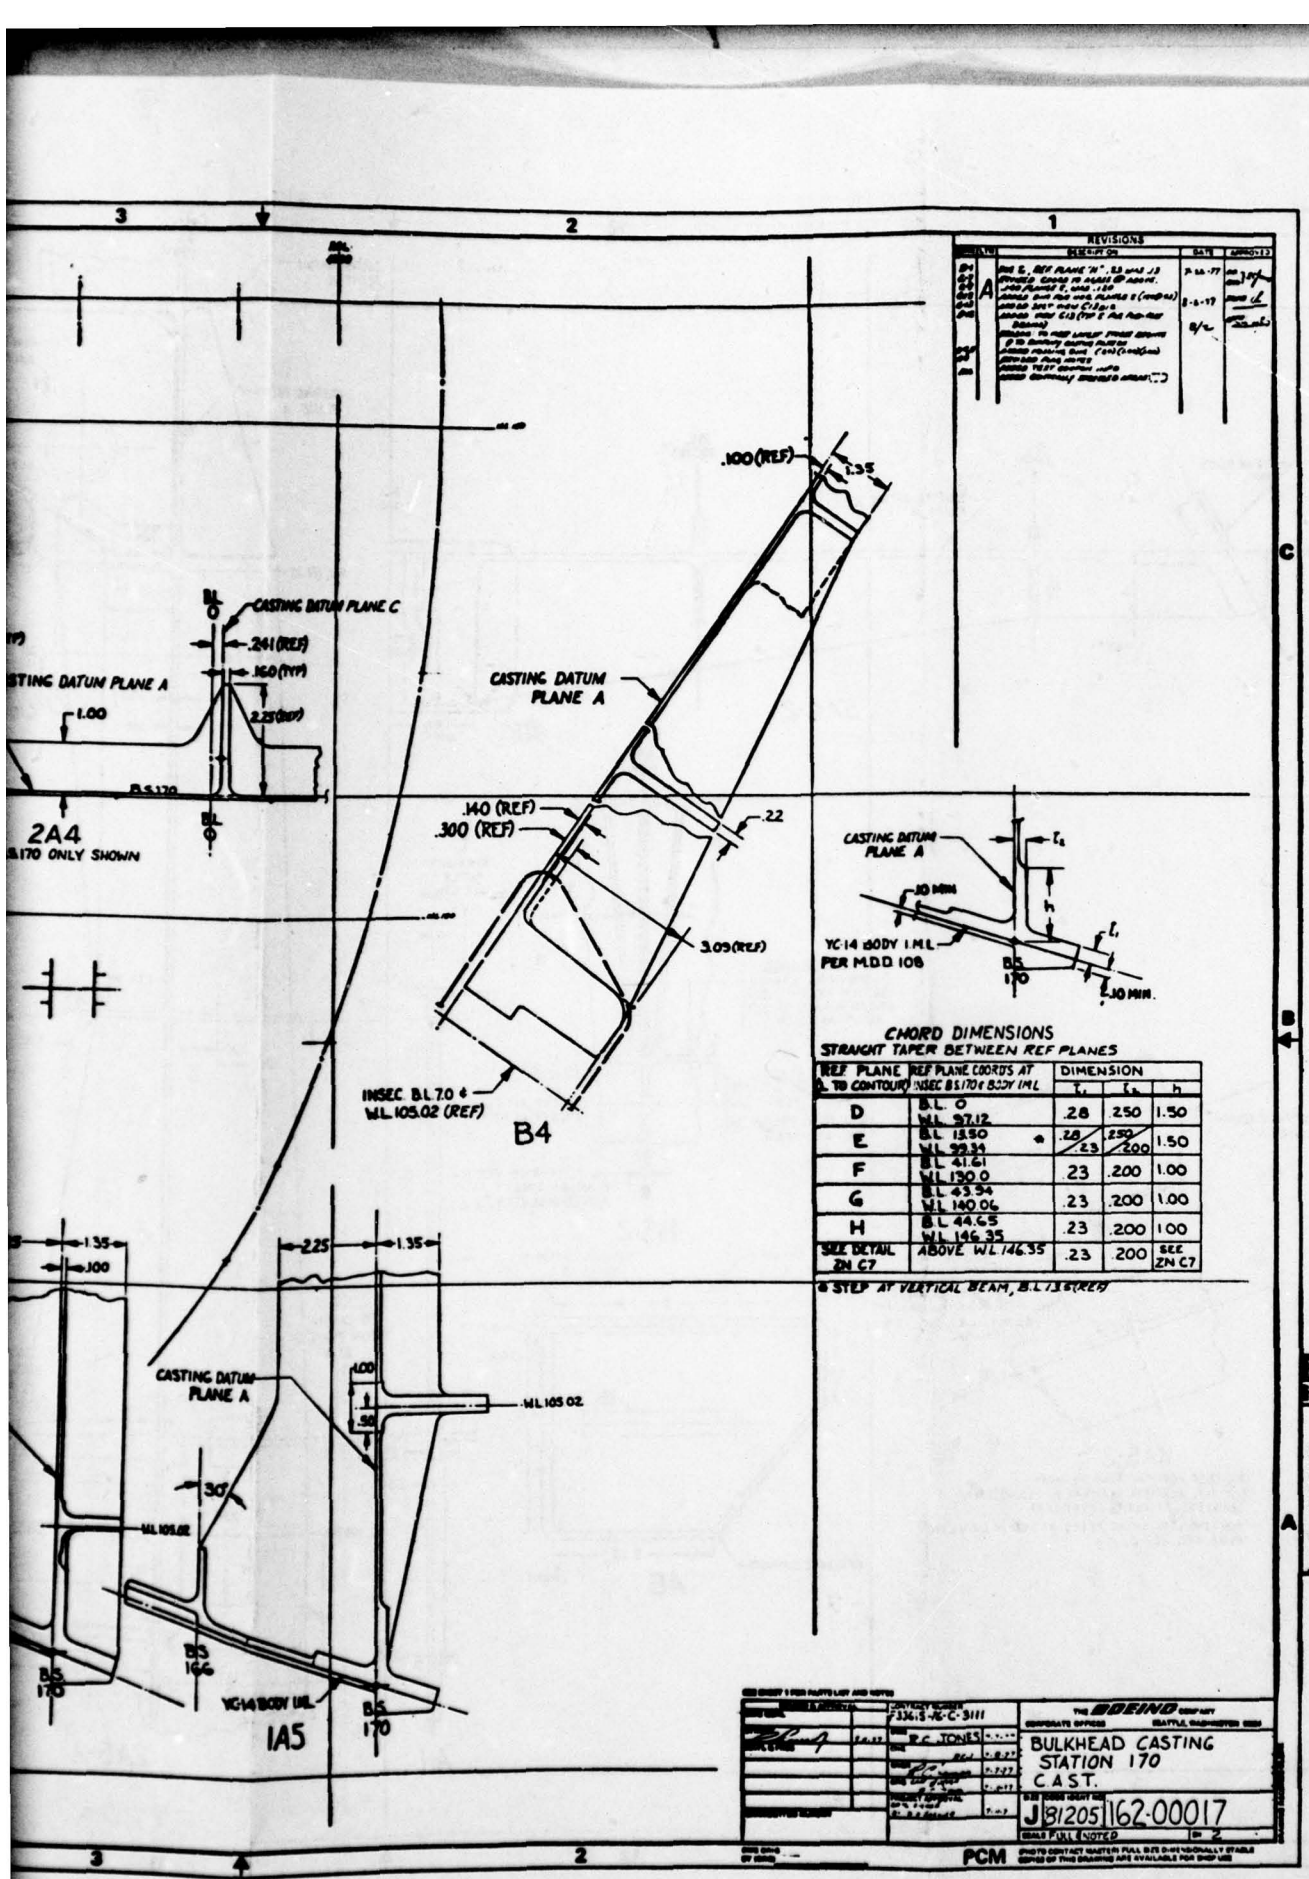
REVISIONS
CASTING DATUM PLANE C
.241 (REF)
.160 (TYP)
2.25 (REF)
CASTING DATUM PLANE A
1.00
B.S. 170
2A4
B.S. 170 ONLY SHOWN
.100 (REF)
1.35
CASTING DATUM PLANE A
.140 (REF)
.300 (REF)
.22
3.09 (REF)
INSEC. B.L. 7.0 ℄
W.L. 105.02 (REF)
B4
CASTING DATUM PLANE A
.10 MIN
YC-14 BODY I.M.L.
PER M.D.D. 108
B.S. 170
.10 MIN.
CHORD DIMENSIONS
STRAIGHT TAPER BETWEEN REF PLANES
REF PLANE TO CONTOUR
REF PLANE COORDS AT INSEC B.S. 170 ℄ BODY I.M.L.
DIMENSION
D
B.L. 0
W.L. 97.12
.28
.250
1.50
E
B.L. 13.50
W.L. 99.34
.28 / .23
.250 / .200
1.50
F
B.L. 41.61
W.L. 130.0
.23
.200
1.00
G
B.L. 43.94
W.L. 140.06
.23
.200
1.00
H
B.L. 44.65
W.L. 146.35
.23
.200
1.00
SEE DETAIL ZN C7
ABOVE W.L. 146.35
.23
.200
SEE ZN C7
@ STEP AT VERTICAL BEAM, B.L. 73 (REF)
1.35
.100
2.25
1.35
CASTING DATUM PLANE A
.100
.50
W.L. 105.02
.30
W.L. 105.02
B.S. 166
B.S. 170
YC-14 BODY I.M.L.
B.S. 170
1A5
F33615-76-C-5111
W.C. JONES
BULKHEAD CASTING
STATION 170
C.A.S.T.
J81205 162-00017
SCALE FULL & NOTED
SHT 2
PCM
9
162-00017 A12
162-00017 S

5

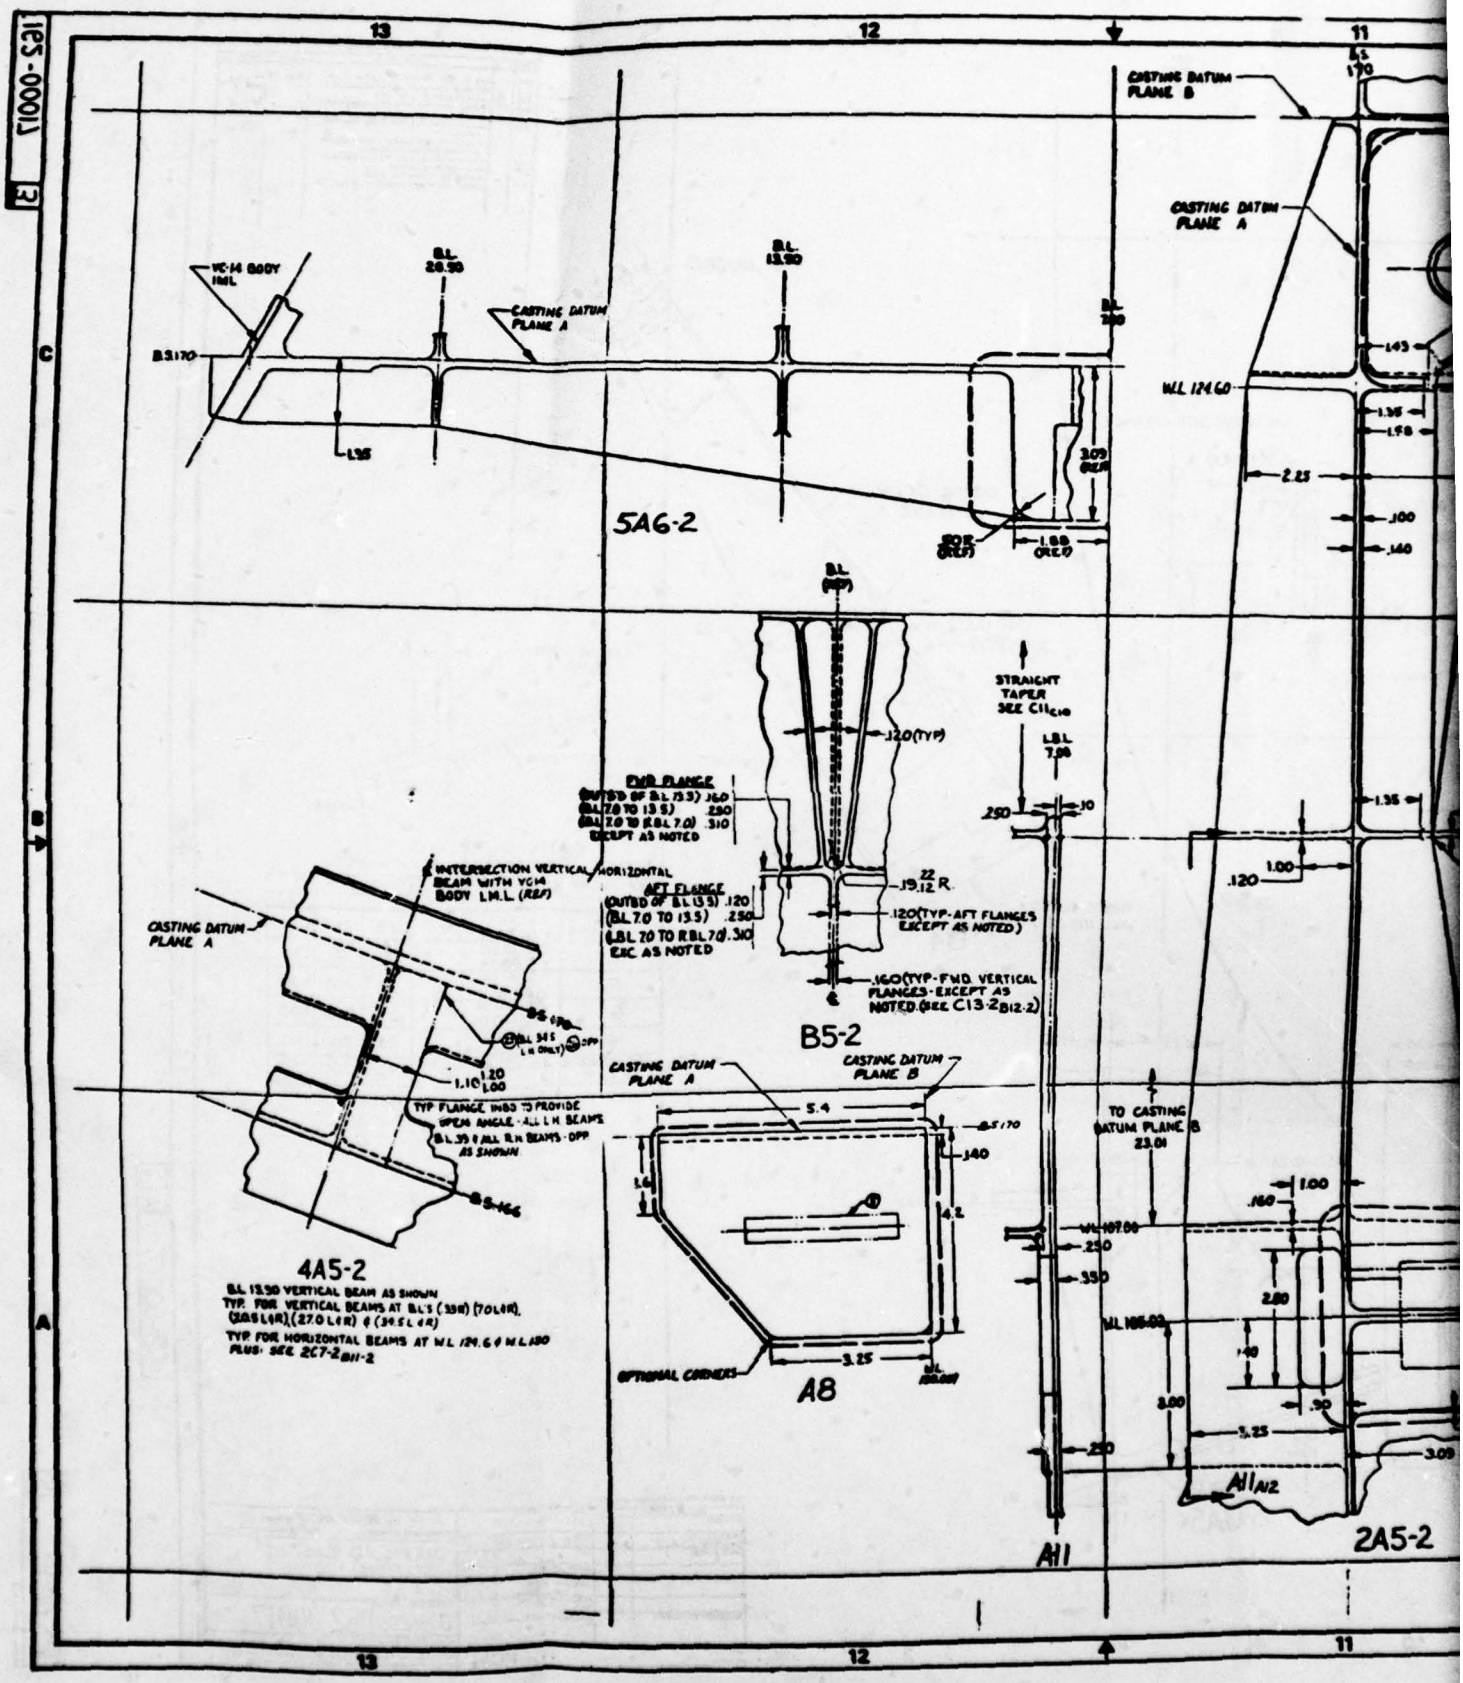
13
12
11
C
B
A
VC-14 BODY INBL
B.S.170
B.L. 28.50
CASTING DATUM PLANE A
B.L. 13.50
B.L. 7.00
L.95
5A6-2
3.09 REF
.825 (REF)
1.88 (REF)
CASTING DATUM PLANE B
W.L. 124.60
1.93
1.35
1.98
2.25
.100
.140
B.L. (REF)
STRAIGHT TAPER SEE C11-2
.120 (TYP)
FWD FLANGE
OUTBD OF B.L. (13.5) .160
(B.L. 7.0 TO 13.5) .250
(B.L. 7.0 TO R B.L. 7.0) .310
EXCEPT AS NOTED
AFT FLANGE
(OUTBD OF B.L. (13.5) .120
(B.L. 7.0 TO 13.5) .250
(L B.L. 7.0 TO R B.L. 7.0) .310
EXC AS NOTED
19.12 R.
.120 (TYP-AFT FLANGES EXCEPT AS NOTED)
.160 (TYP-FWD VERTICAL FLANGES-EXCEPT AS NOTED. (SEE C13-2 B12-2)
B5-2
L.B.L. 7.00
.250
.10
1.35
1.00
.120
INTERSECTION VERTICAL BEAM WITH VC14 BODY LM.L. (REF)
CASTING DATUM PLANE A
B.L. 39.5 (L.H. ONLY) OPP
1.10
1.20
1.00
TYP FLANGE INBD TO PROVIDE SPEAR ANGLE - ALL L.H. BEAMS B.L. 39.5 & ALL R.H. BEAMS - OPP AS SHOWN
B.S.166
4A5-2
B.L. 13.50 VERTICAL BEAM AS SHOWN
TYP. FOR VERTICAL BEAMS AT B.L.'S (39R) (70L&R), (120.5 L&R), (27.0 L&R) & (39.5 L&R)
TYP FOR HORIZONTAL BEAMS AT W.L. 124.6 & W.L. 130 PLUS- SEE 2C7-2 B11-2
CASTING DATUM PLANE A
CASTING DATUM PLANE B
5.4
B.S.170
.140
1.4
4.2
OPTIONAL CORNERS
3.25
B.L. 80.00
A8
TO CASTING DATUM PLANE B 23.01
1.00
.160
W.L. 107.00
.250
.350
2.80
W.L. 105.00
.140
.50
3.00
5.25
.250
3.09
A11
A12
2A5-2
A11

162-00017 A 3

2

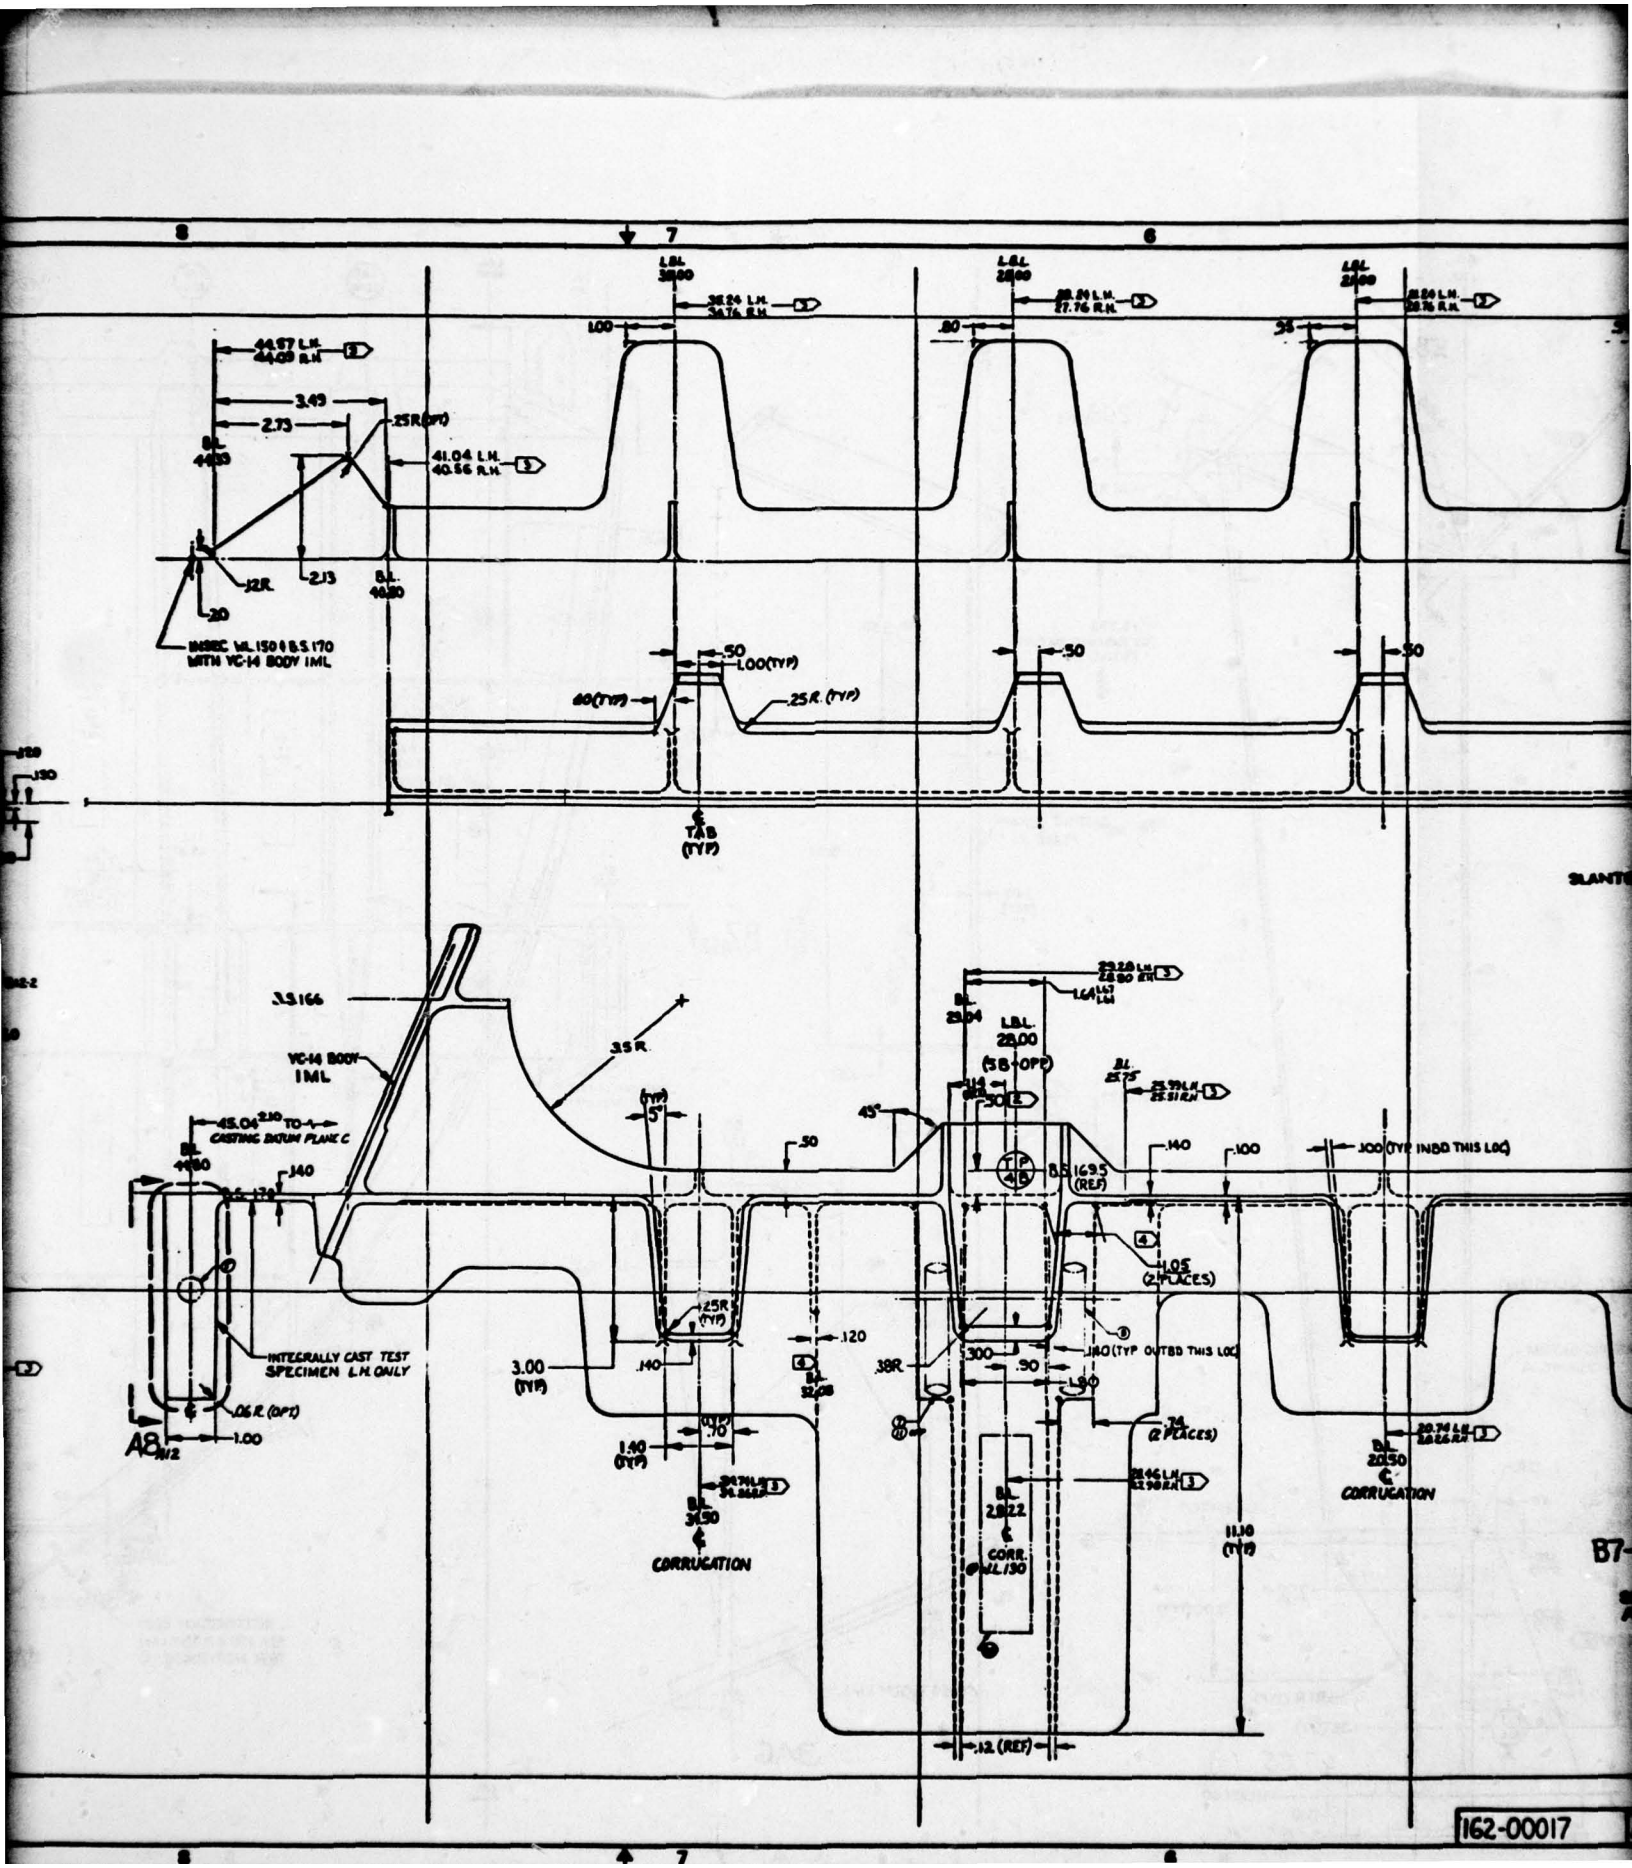
8
7
6
INSRC WL 150 & BS 170 WITH VC-14 BODY IML
VC-14 BODY IML
CASTING DATUM PLANE C
INTEGRALLY CAST TEST SPECIMEN L.H. ONLY
CORRUGATION
CORRUGATION
CORR. @ WL 130
TAB (TYP)
(2 PLACES)
(2 PLACES)
(TYP OUTBD THIS LOC)
(TYP INBD THIS LOC)
(REF)
(TYP)
(TYP)
(TYP

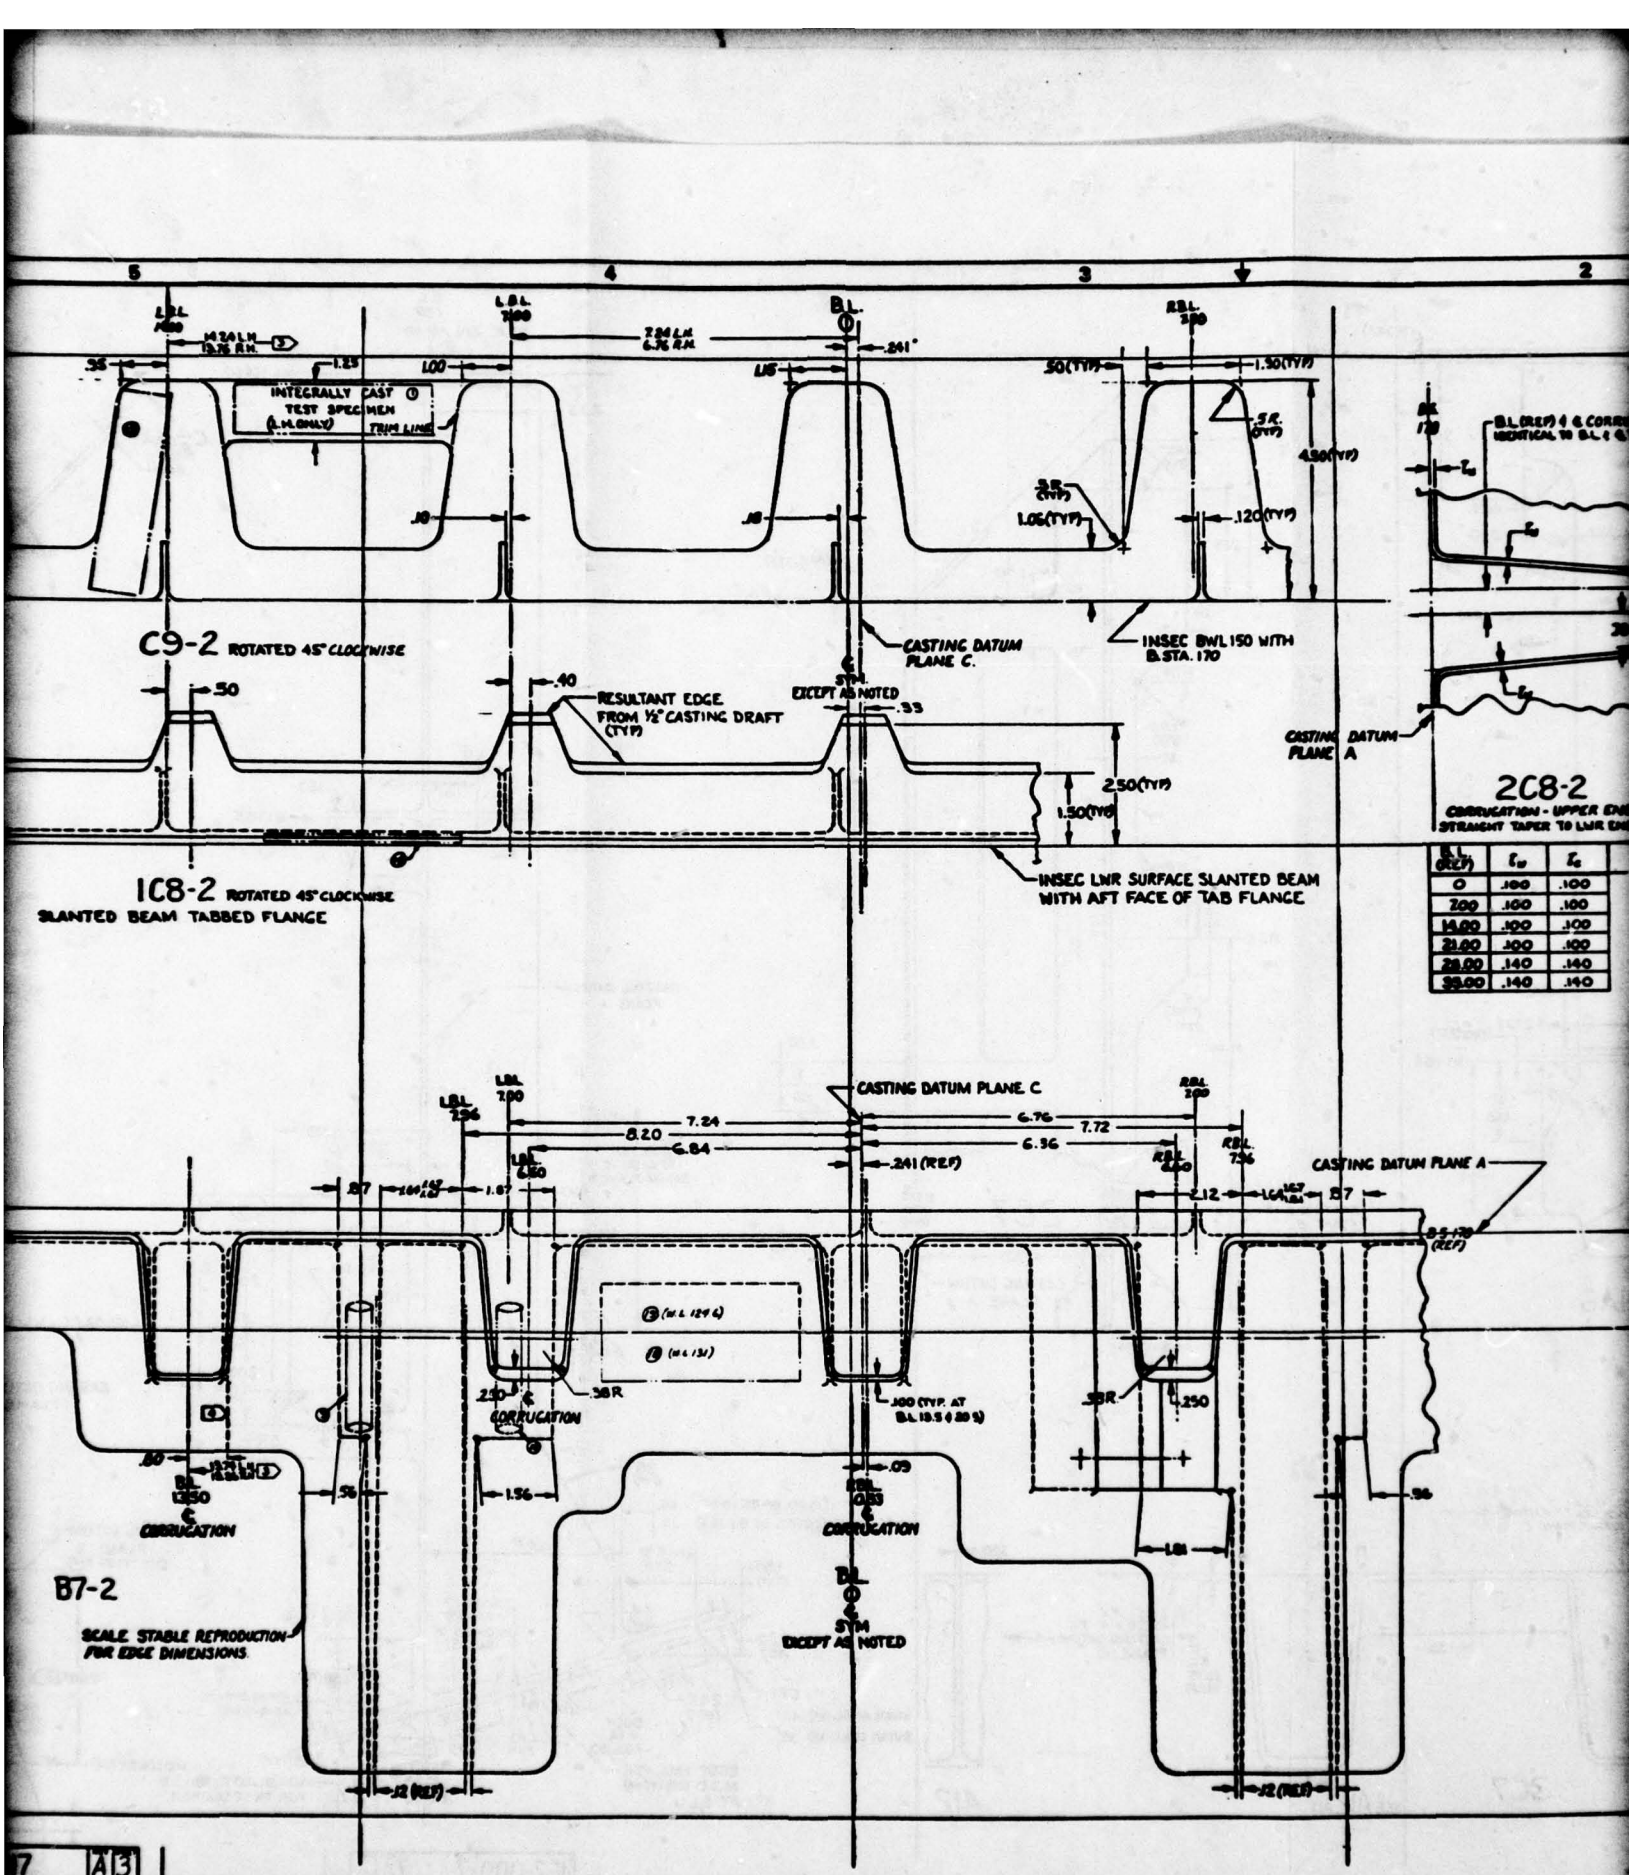

B.L. (REF)	t_w	t_f
0	.100	.100
7.00	.100	.100
14.00	.100	.100
21.00	.100	.100
28.00	.140	.140
35.00	.140	.140

4

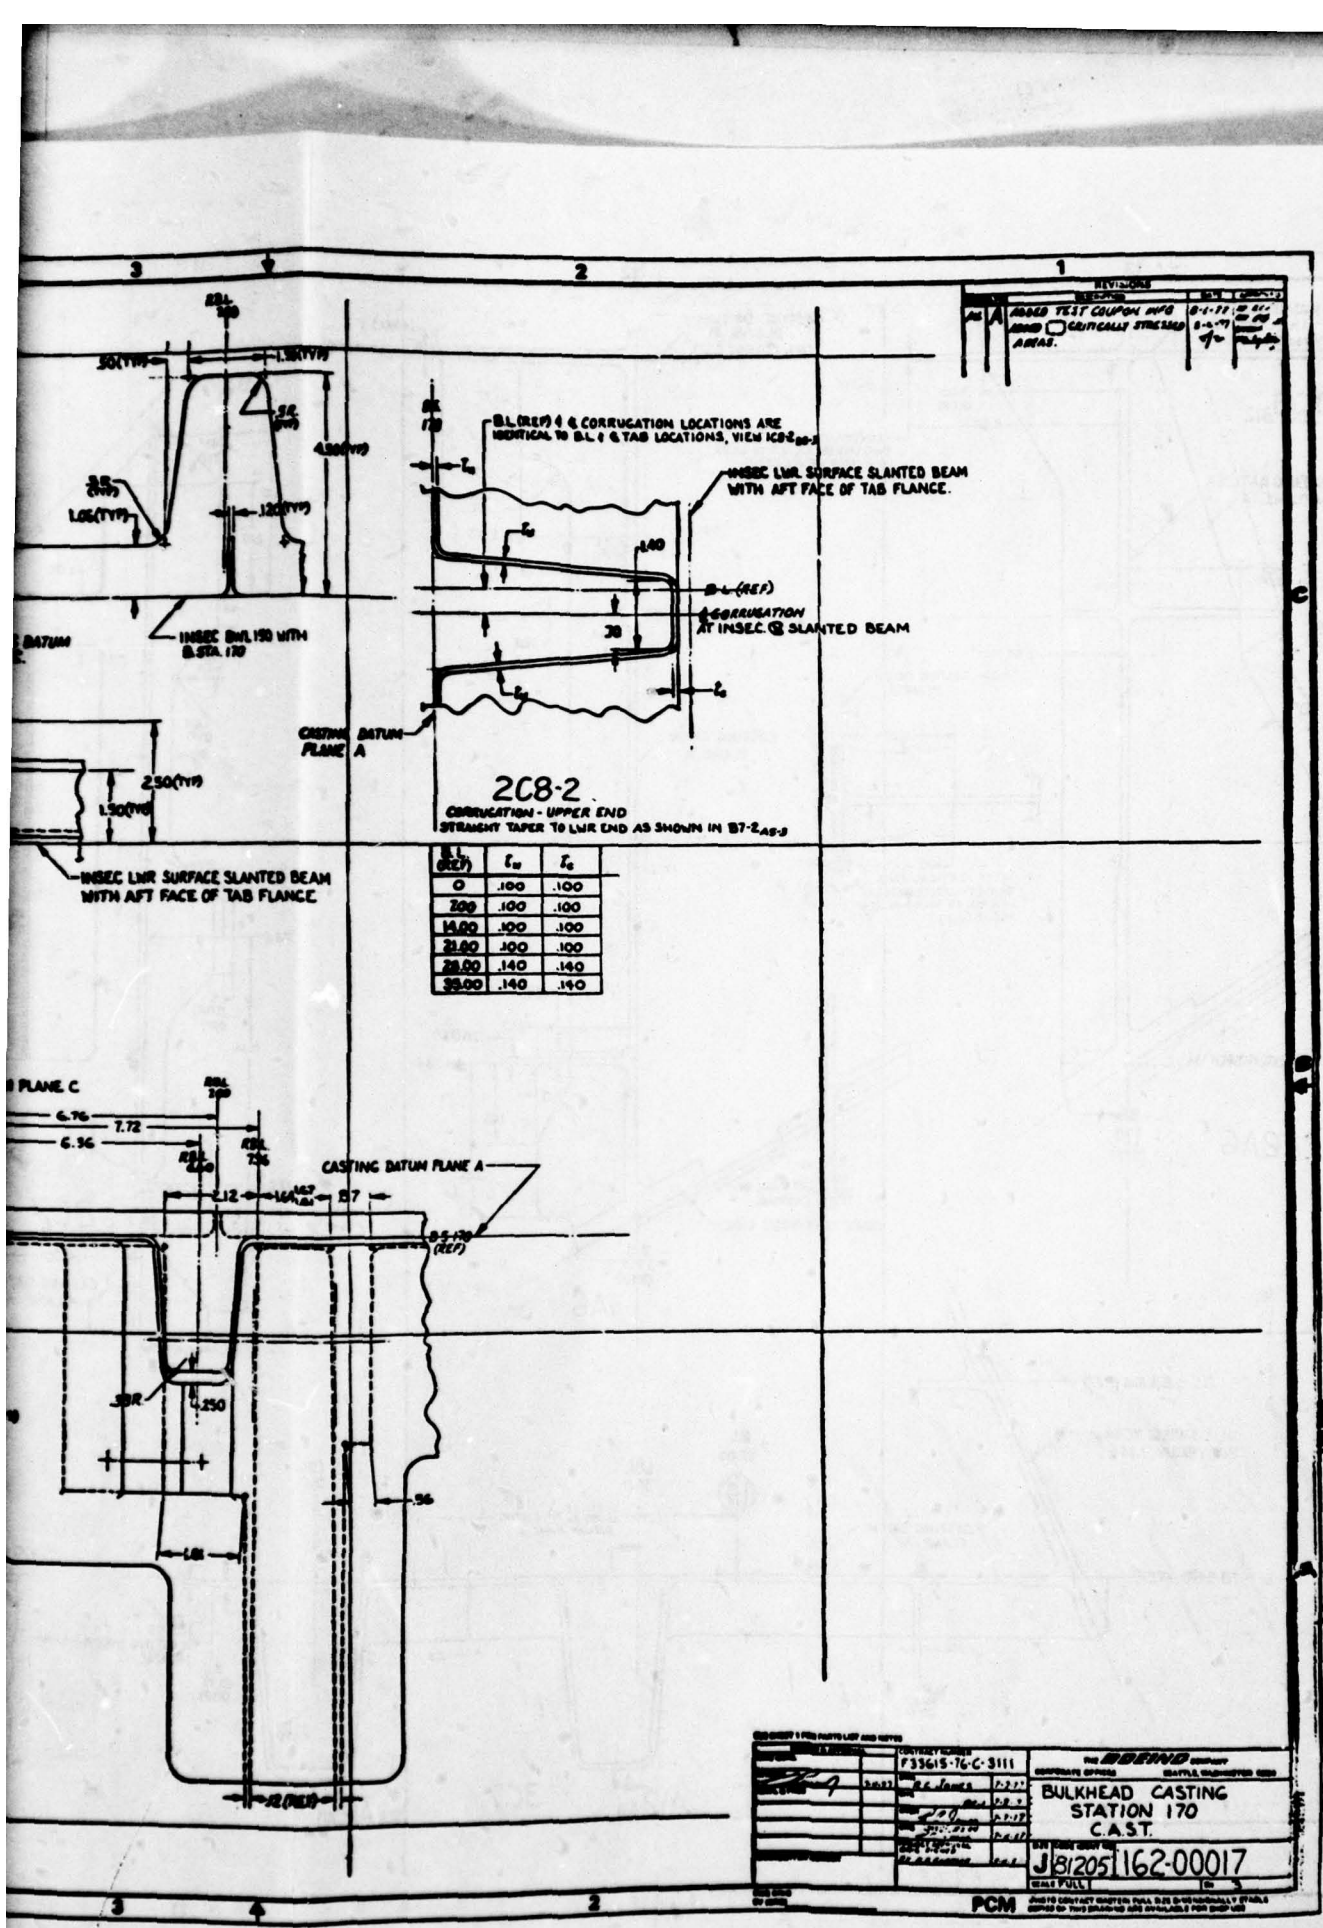

B.L. (REF)	t_w	t_o
0	.100	.100
7.00	.100	.100
14.00	.100	.100
21.00	.100	.100
28.00	.140	.140
35.00	.140	.140

10

5

A 71000-251
9
8
7
C
B
A
9
8
7

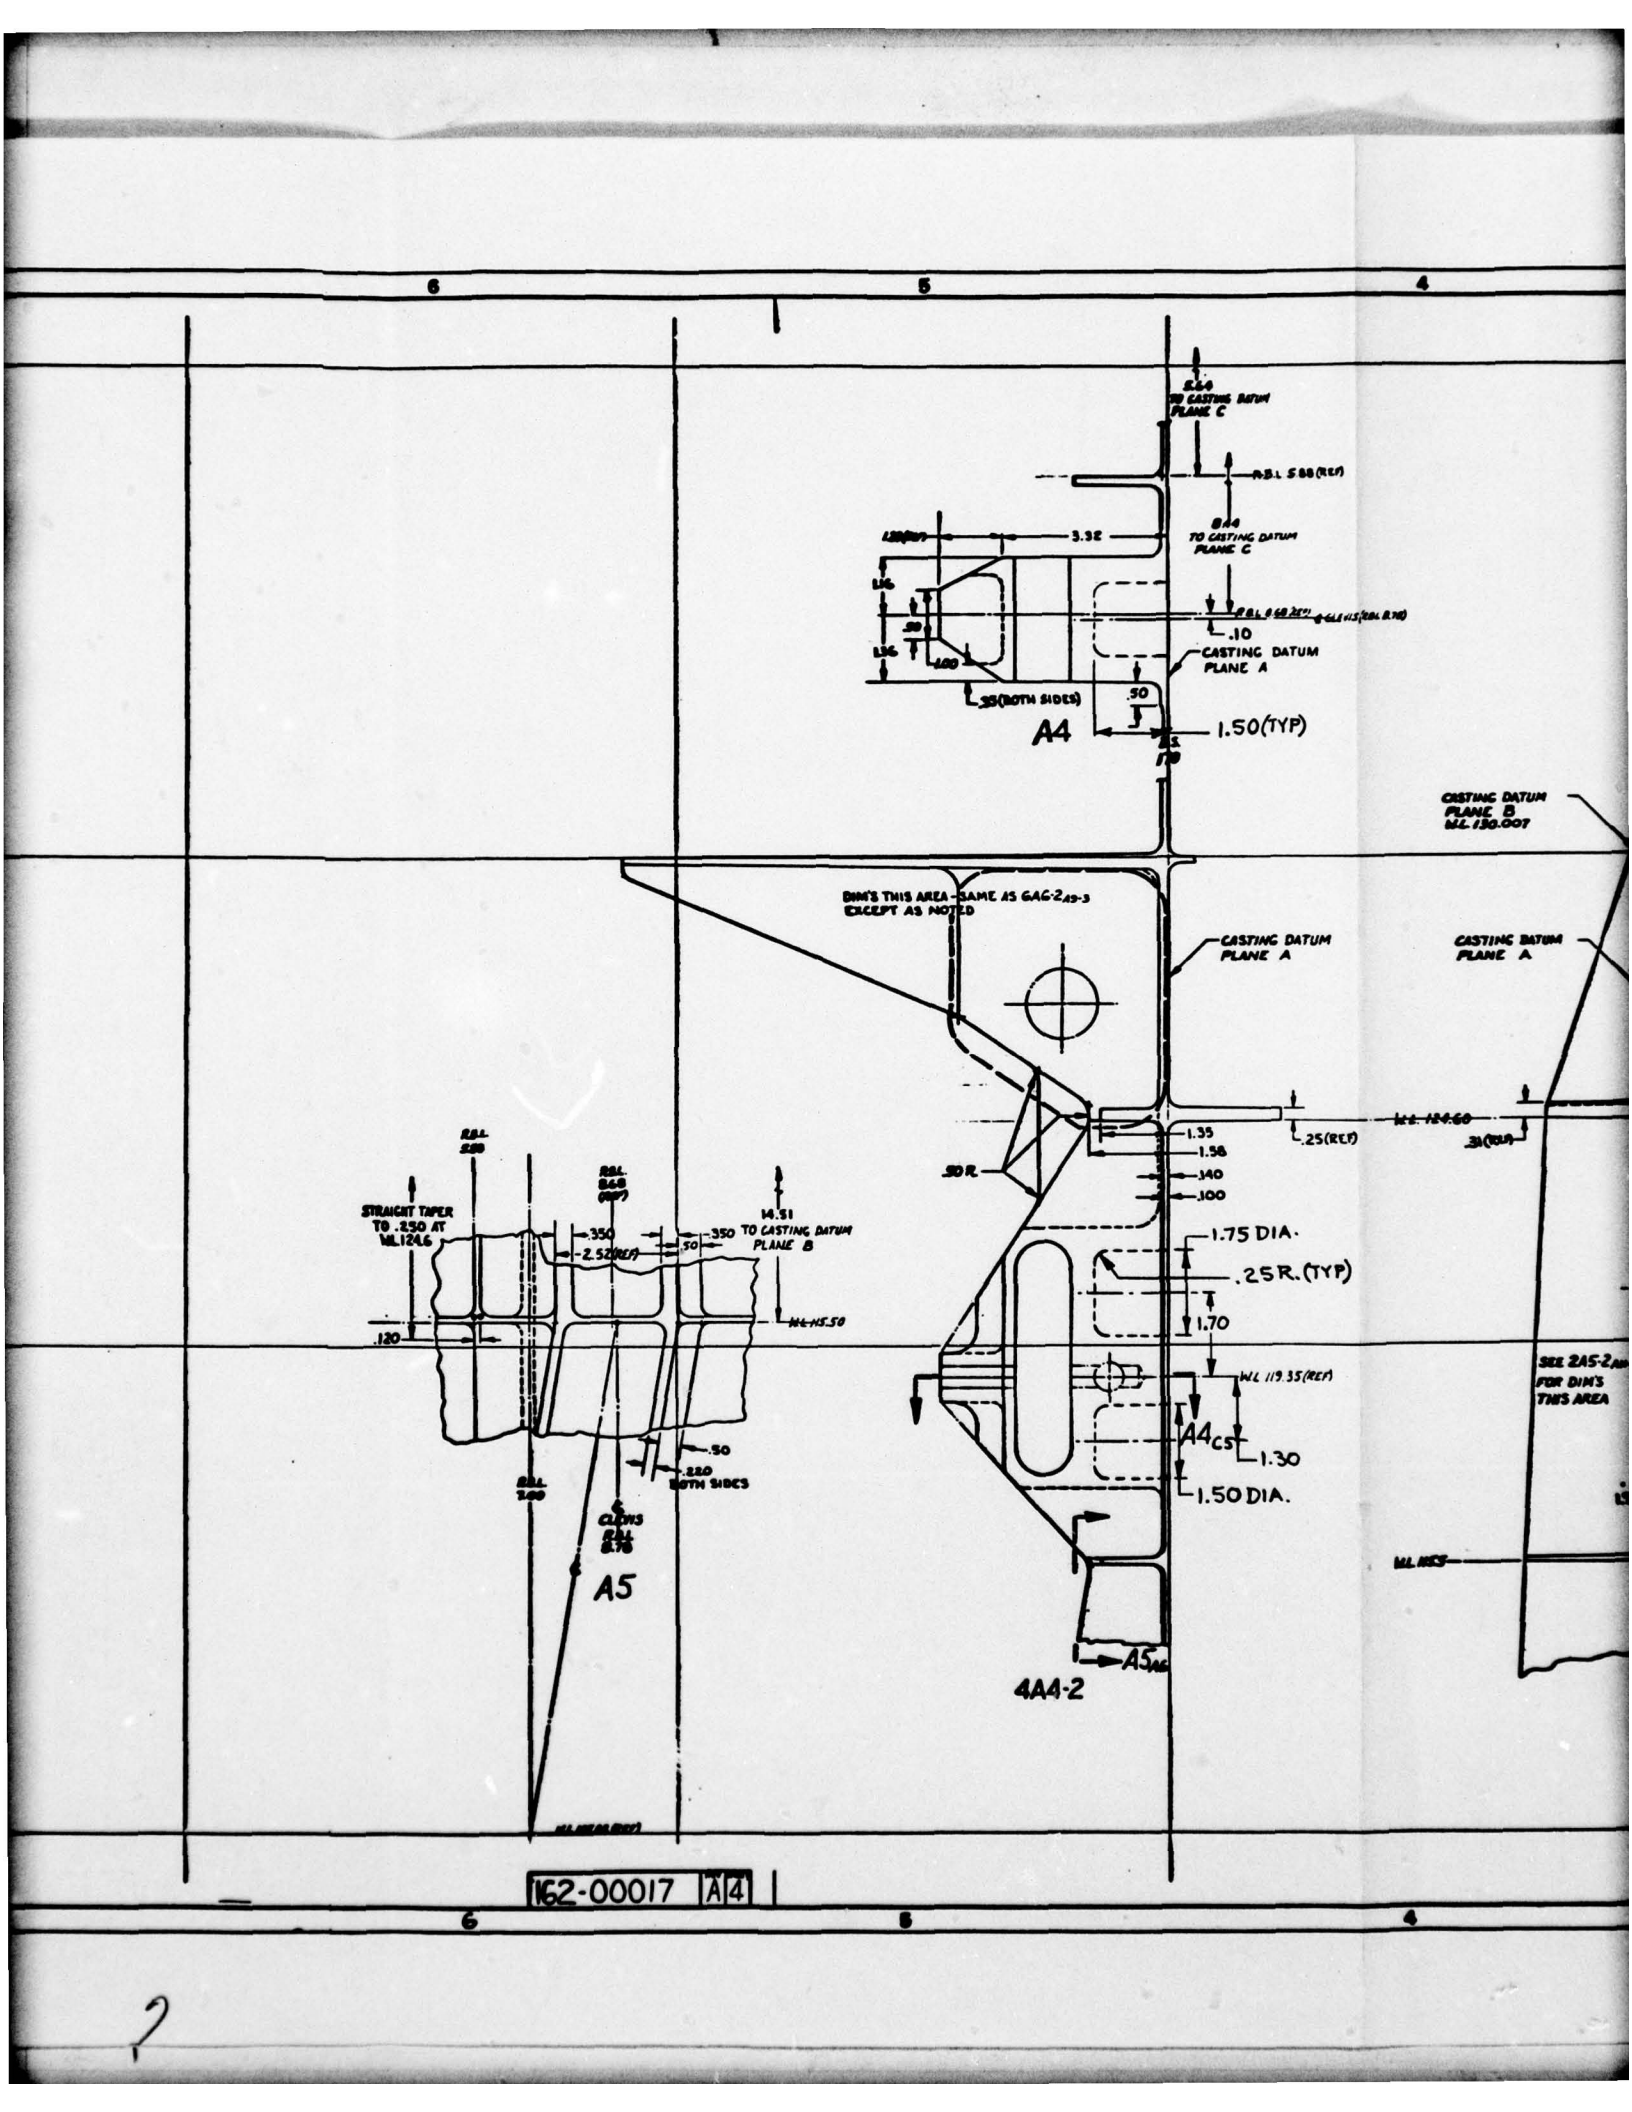
6
5
4
3.38
.10
CASTING DATUM PLANE A
.50
1.50(TYP)
A4
CASTING DATUM PLANE B
WL 130.007
DIM'S THIS AREA - SAME AS GAG-2 A9-3 EXCEPT AS NOTED
CASTING DATUM PLANE A
CASTING DATUM PLANE A
1.35
1.58
.140
.100
.50R.
.25(REF)
1.75 DIA.
.25R.(TYP)
1.70
WL 119.35(REF)
A4 CS
1.30
1.50 DIA.
A5 AC
4A4-2
SEE 2A5-2 A
FOR DIM'S THIS AREA
WL 114.50
STRAIGHT TAPER TO .250 AT WL 124.6
.350
2.52(REF)
.350
.50
14.51 TO CASTING DATUM PLANE B
WL 115.50
.120
.50
.220 BOTH SIDES
A5
162-00017 A4
6
5
4

2

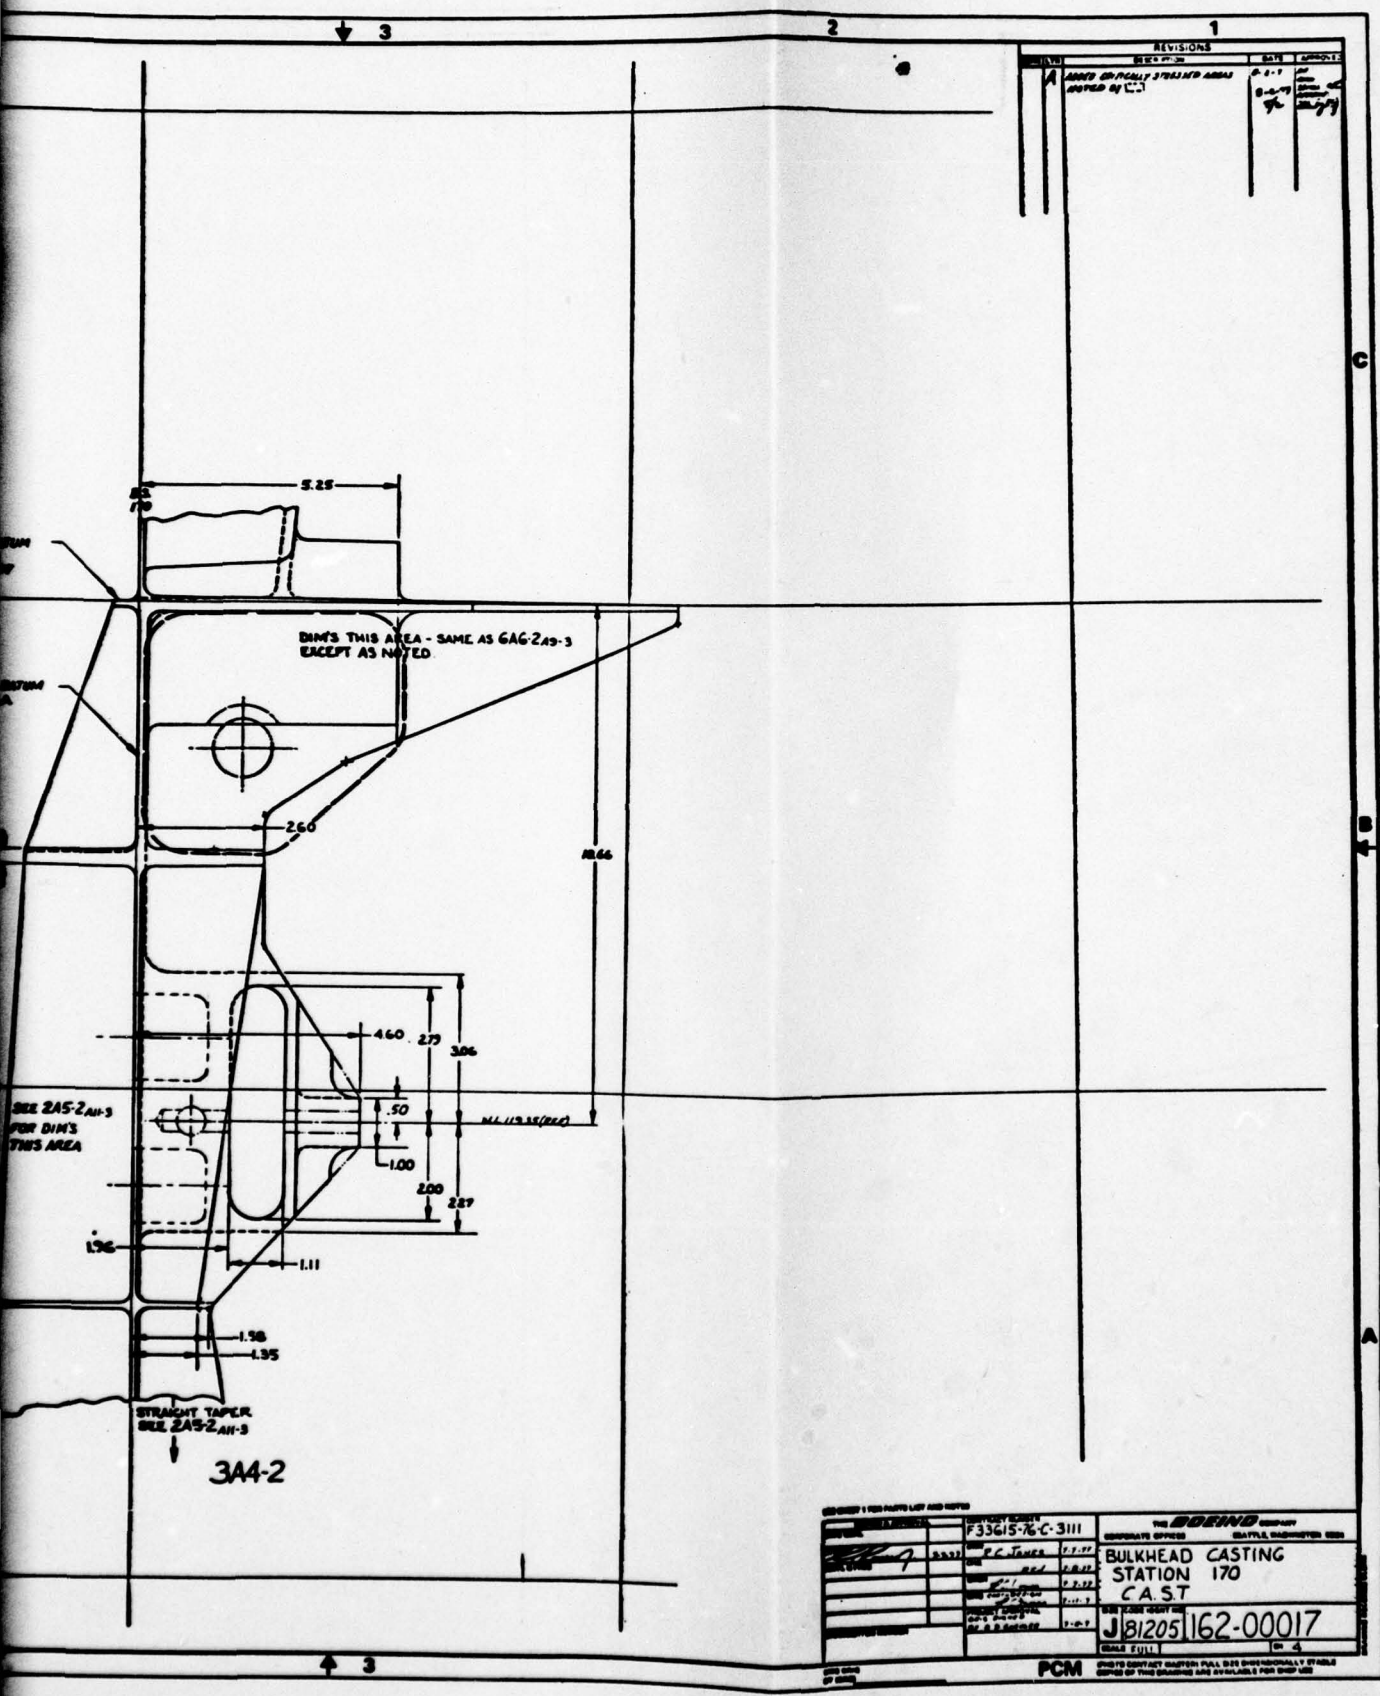
REVISIONS
DIM'S THIS AREA - SAME AS GAG-2A9-3 EXCEPT AS NOTED
5.25
2.60
18.66
4.60
2.79
3.06
.50
1.00
2.00
2.27
1.96
1.11
1.98
1.95
SEE 2A5-2AH-3 FOR DIM'S THIS AREA
STRAIGHT TAPER SEE 2A5-2AH-3
3A4-2
F33615-76-C-3111
BULKHEAD CASTING
STATION 170
C.A.S.T
J81205 162-00017
SCALE FULL
PCM
162-00017 A14
1ES-00017 A

81000-S2I
6
5
4
D
C
B
A
-1
162-00001
TEST ONLY
APPLICATION

NOTES

1. [illegible]

(10) DATUM TABLET FT. DIM. GENL DWG TOL. DOES NOT APPLY.

(11) NAS 77400-08P BUSHINGS ARE OPTIONAL TO BAC B28A08M0808 IN EQUIV. DIA & LENGTH.

(12) STEP RESULTING FROM CASTING DRAFT.

2 125 ALL MACHINED SURFACES EXCEPT AS NOTED

6. BREAK ALL SHARP EDGES .03-.22.

(13) INSTALL BUSHINGS WITH WET PRIMER (TT-P-29) PER BAC 5436

(14) CASTING REFERENCE ONLY

(15) ALL HOLES ON THIS & THRU THE LANDING GEAR FITTING LUGS TO BE CONCENTRIC WITHIN .002.

(16) SPOTFACE 1.75 DIA. FLAT, .05-.07 FILLET RADIUS, ONLY AS REQ'D TO PROVIDE FLAT SURFACE FOR BUSHING FLANGE, .1 MAX DEPTH.

(17) PENETRANT INSPECT MACHINED SURFACES PER BAC 5423.

REV STATUS

LTR	
2	
3	
4	

REVISIONS

ZONE (LTR)	DESCRIPTION	DATE	APPROVED

			4		BAC B28B20M090	BUSHING (3)	C9-3					
			2		BAC B28B20M075	BUSHING (3)	C9-3					
			2		BAC B28B16M095	BUSHING (3)	B5-4					
			2		BAC B28B16M085	BUSHING (3)	C9-3					
			1		-2	BULKHEAD	A4-2	MAKE FROM 162-30017-1 (11)		—	FIT 04	R
			-		-1	BULKHEAD ASSY.				—		R

PARTS LIST

ITEM	SHOW IN ASSY	QTY REQ	FIND NUMBER	PART OR IDENTIFYING NUMBER	NOMENCLATURE OR DESCRIPTION	ZONE	MATERIAL AND SPECIFICATION	ORDER UNIT OF	QTY PER	FINISH	QTY PER ASSY	REV LTR

DIMENSIONING & TOLERANCING PER ANSI Y14.5

UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES

TOLERANCES: FRACTIONS ±1/64 DECIMALS .XX ±.03 DECIMALS .XXX ±.010 ANGLES ± 0° 30' 0" SURFACE FINISH 125 OR BETTER, UNLESS OTHERWISE NOTED

BREAK SHARP EDGES .01 TO .03 OR 0.5 TO 1.0 MM OR 0.5 MM OR GREATER

DRAWN WITH SOLIDWORKS 2009

QTY	1	2	3	4

PART OR IDENTIFYING NUMBER CODES

DRAWN	
DESIGN	
STRESS	
MATERIALS	
PROCESS	
PROJECT ENGINEER	
CHECKED	
CONTRACTOR NUMBER	

CONTRACT NUMBER F33615-76-C-3111

DRAWN	C. JAMES	8/11/77
DESIGN	[illegible]	8/11/77
STRESS	—	—
MATERIALS	[illegible]	9-7-77
PROCESS	[illegible]	9-16-77
PROJECT ENGINEER	[illegible]	

THE BOEING COMPANY

CORPORATE OFFICES SEATTLE, WASHINGTON 98124

BULKHEAD ASSEMBLY
STATION 170
C.A.S.T

SIZE J | CAGE IDENT NO 81205 | 162-00018

SCALE — | SHEET 1 OF 4

162-00018 | REV 11

162-00018 | 11

13

2

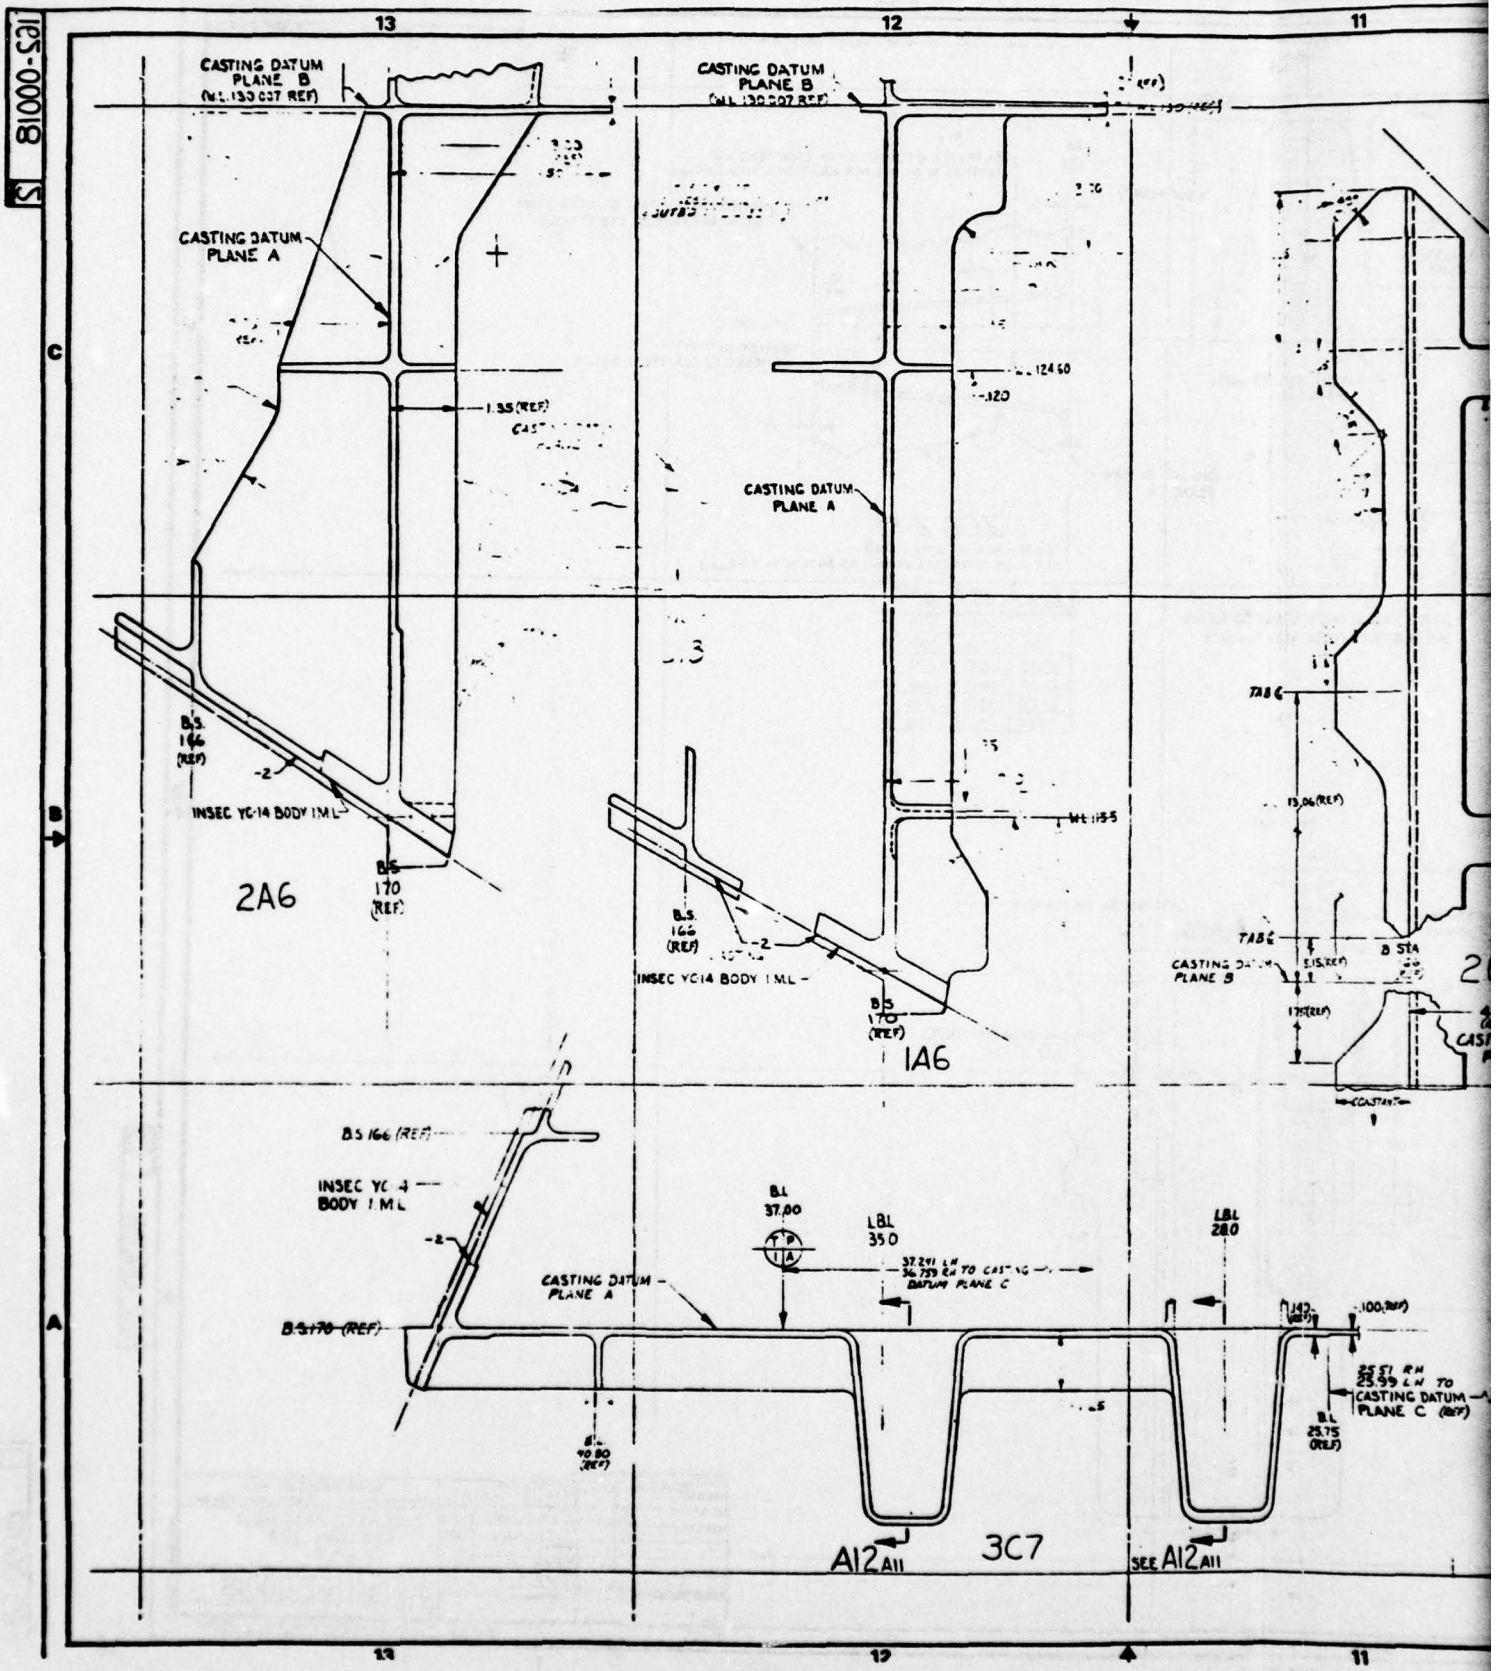
81000-SA1
13
12
11
CASTING DATUM PLANE B (W.L. 130.037 REF)
CASTING DATUM PLANE B (W.L. 130.507 REF)
CASTING DATUM PLANE A
CASTING DATUM PLANE A
1.35 (REF)
124.60
120
B.S. 166 (REF)
-2
INSEC YC-14 BODY I.M.L.
B.S. 170 (REF)
2A6
W.L. 155
1A6
TAB C
13.06 (REF)
TAB E
B STA
CASTING DATUM PLANE B
B.S. 166 (REF)
INSEC YC-14 BODY I.M.L.
B.L. 37.00
LBL 35.0
LBL 28.0
CASTING DATUM PLANE A
B.S. 170 (REF)
37.291 LH 36.739 RH TO CASTING DATUM PLANE C
25.51 RH 25.99 LH TO CASTING DATUM PLANE C (REF)
B.L. 25.75 (REF)
B.L. 40.80 (REF)
A12 A11
3C7
SEE A12 A11
12
11

10
9
8
BS 170
SEE ZN A8-A9
W.L. 124.60
C9 C5-3
1C8 B5-3
2C8 C2-3
22½° (REF)
45° (REF)
W.L. 150
19.993
TO CASTING DATUM PLANE B
W.L. 115.5
CASTING DATUM PLANE A
W.L. 139
8.993
TO CASTING DATUM PLANE
2C7
4.00 (REF)
CASTING DATUM PLANE A
W.L. 107.00
24.987
TO CASTING DATUM PLANE B
W.L. 105.02
W.L. 135 (REF)
CASTING DATUM PLANE A
CASTING DATUM PLANE B
(W.L. 130.007 REF)
1.50 (TYP)
.20 (TYP)
1.60
.20 R.
UNBD OF BL 13.5) .20
OUTBD OF BL 13.5) .15
BODY STA 166.00
BODY STA 170.00
BODY I.M.L. PER M.B.D. 108 (YC-14) AT B.L.O
1.50 (REF)
.28 (REF)
.30 (REF)
4.007
.75
W.L. 126.00 (REF)
3.20 (TYP)
A12
1A4
C5
W.L. 124.60
SEE ZN D10
162-00018
12
10
9
8

2

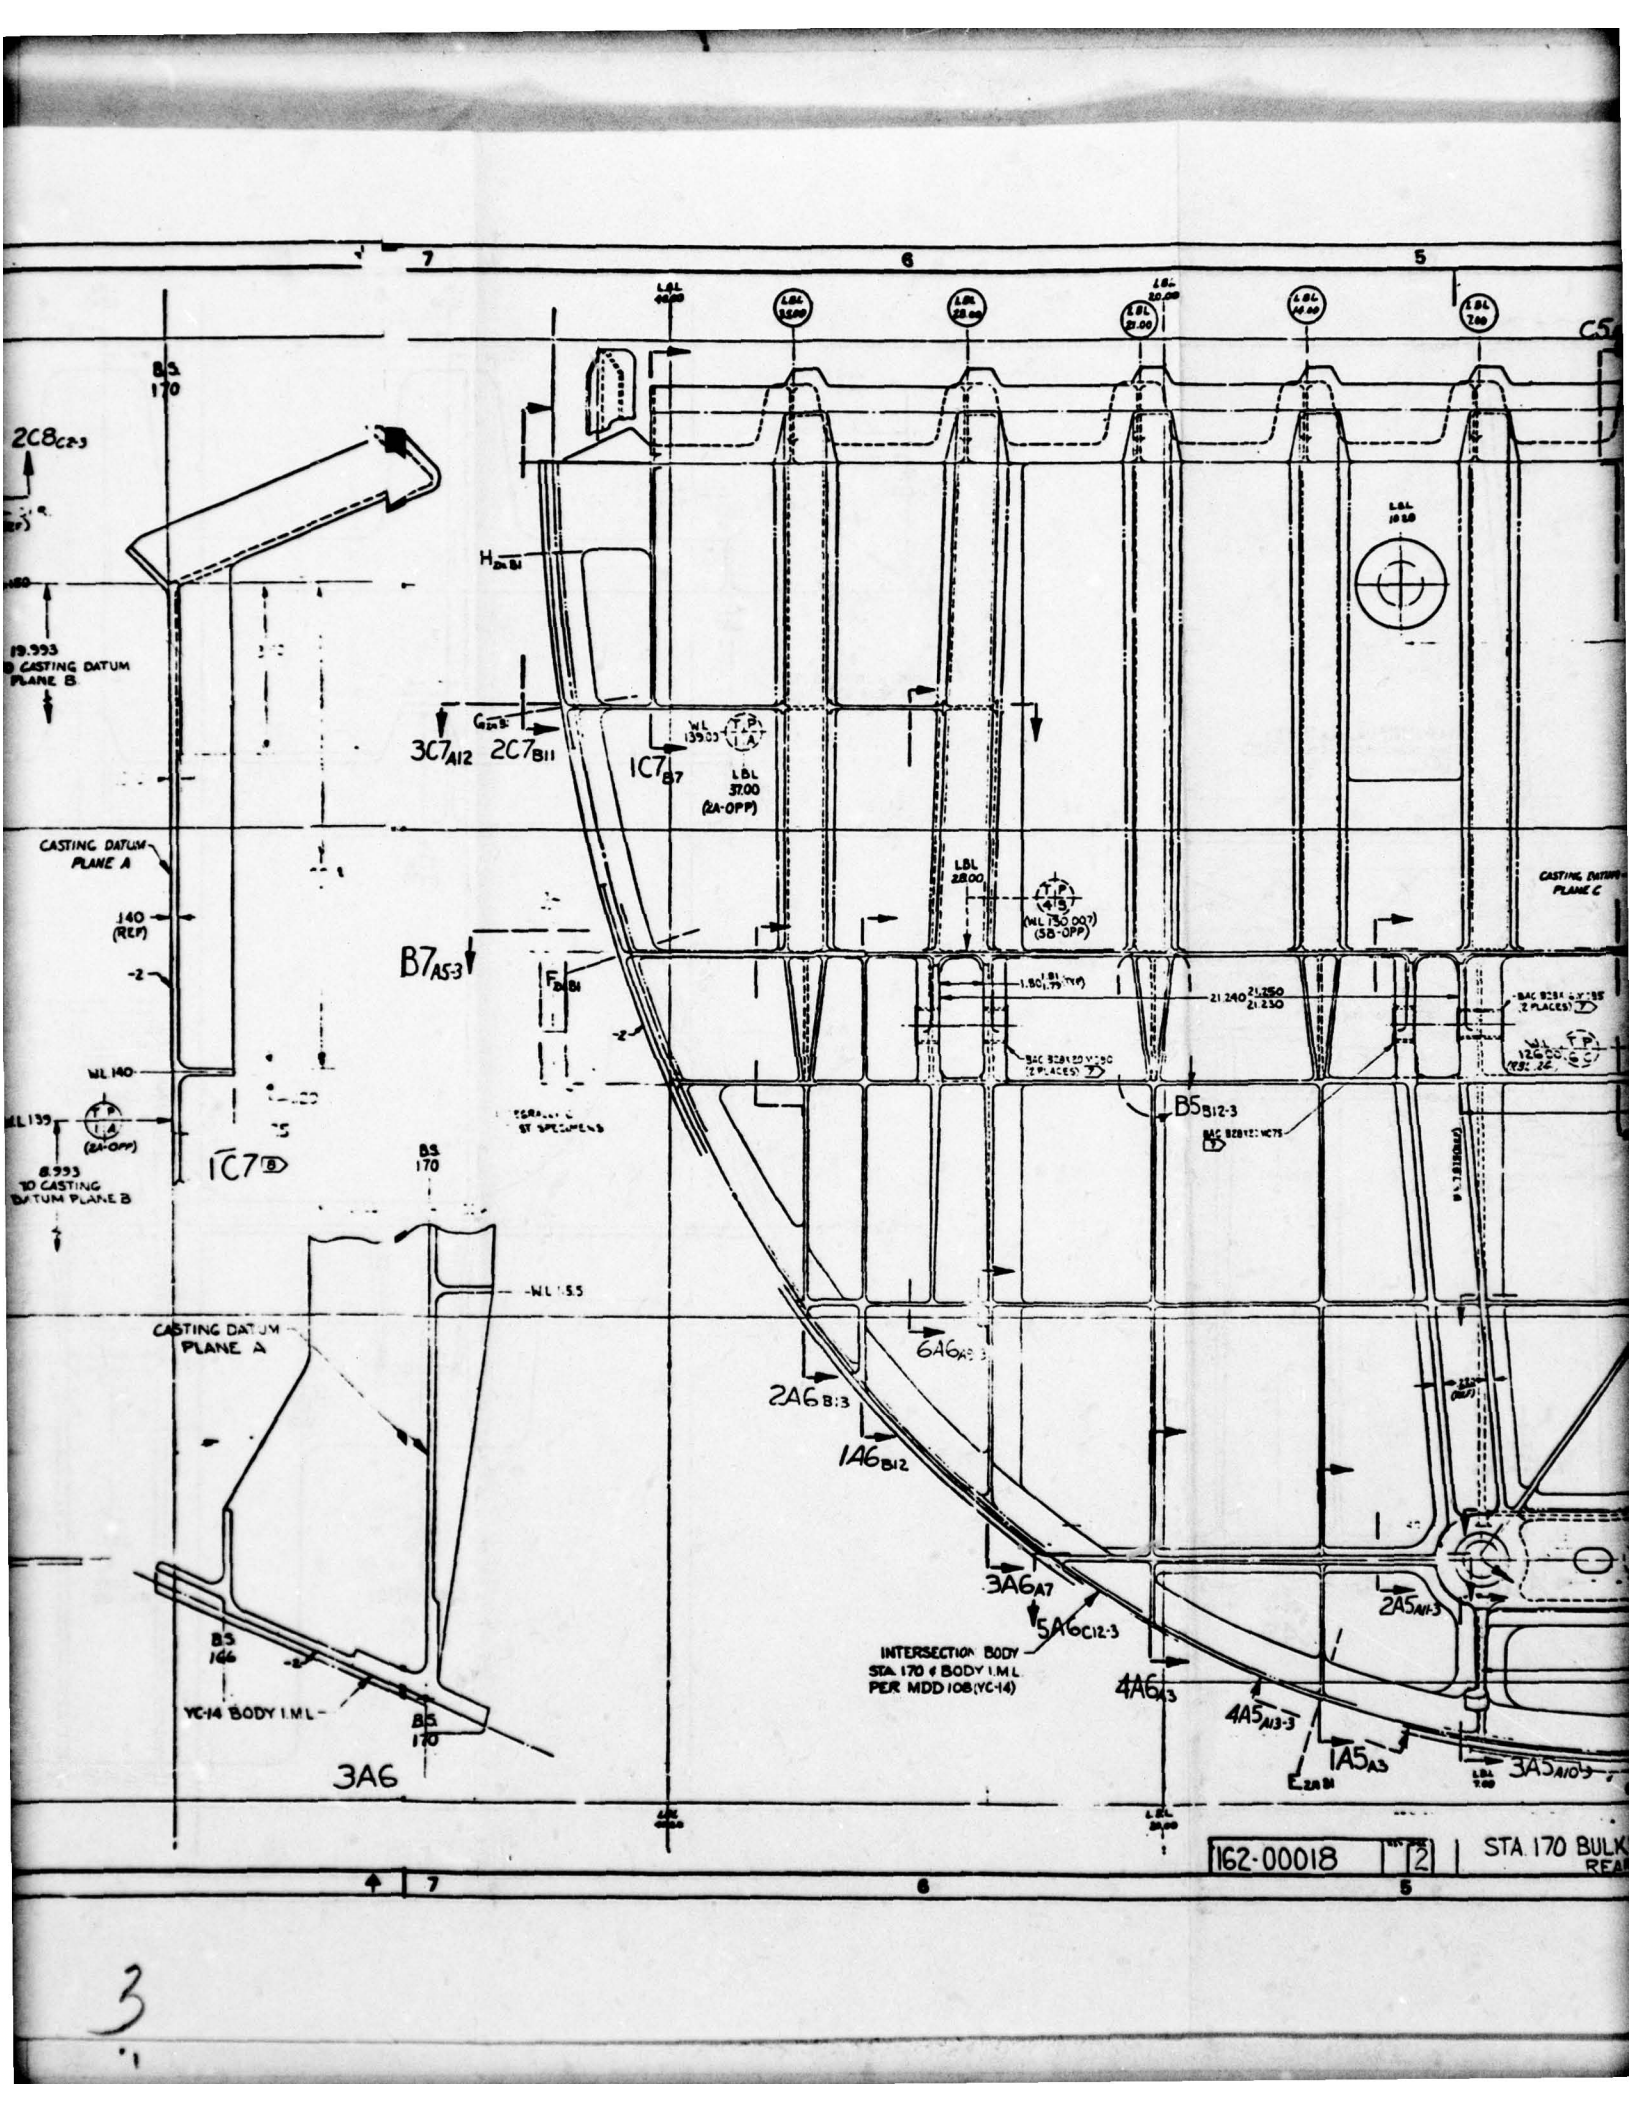
7
6
5
BS 170
2C8 C2-3
19.993 B CASTING DATUM PLANE B
CASTING DATUM PLANE A
140 (REF)
-2
WL 140
WL 139
8.993 TO CASTING DATUM PLANE B
1C7 B
BS 170
WL 155
CASTING DATUM PLANE A
BS 146
-2
YC-14 BODY I.M.L.
BS 170
3A6
3C7 A12
2C7 B11
H 2R B1
G 2R B1
1C7 B7
LBL 37.00 (2A-OPP)
WL 139.00
T.P. 1A
B7 A5-3
F 2R B1
LBL 28.00
T.P. 4B
(WL 130.007) (3B-OPP)
1.80
21.240
21.250
21.230
BAC B28B20 V100 (2 PLACES)
B5 B12-3
BAC B28B12 V075
WL 126.00 (REF. 2C)
2A6 B13
1A6 B12
6A6 A9
3A6 A7
5A6 C12-3
INTERSECTION BODY STA 170 & BODY I.M.L. PER MDD 108 (YC-14)
4A6 A13
4A5 A13-3
1A5 A3
2A5 A11-3
3A5 A10-3
LBL 10.00
LBL 20.00
LBL 7.00
C5
CASTING DATUM PLANE C
162-00018
2
STA 170 BULK
REA

3

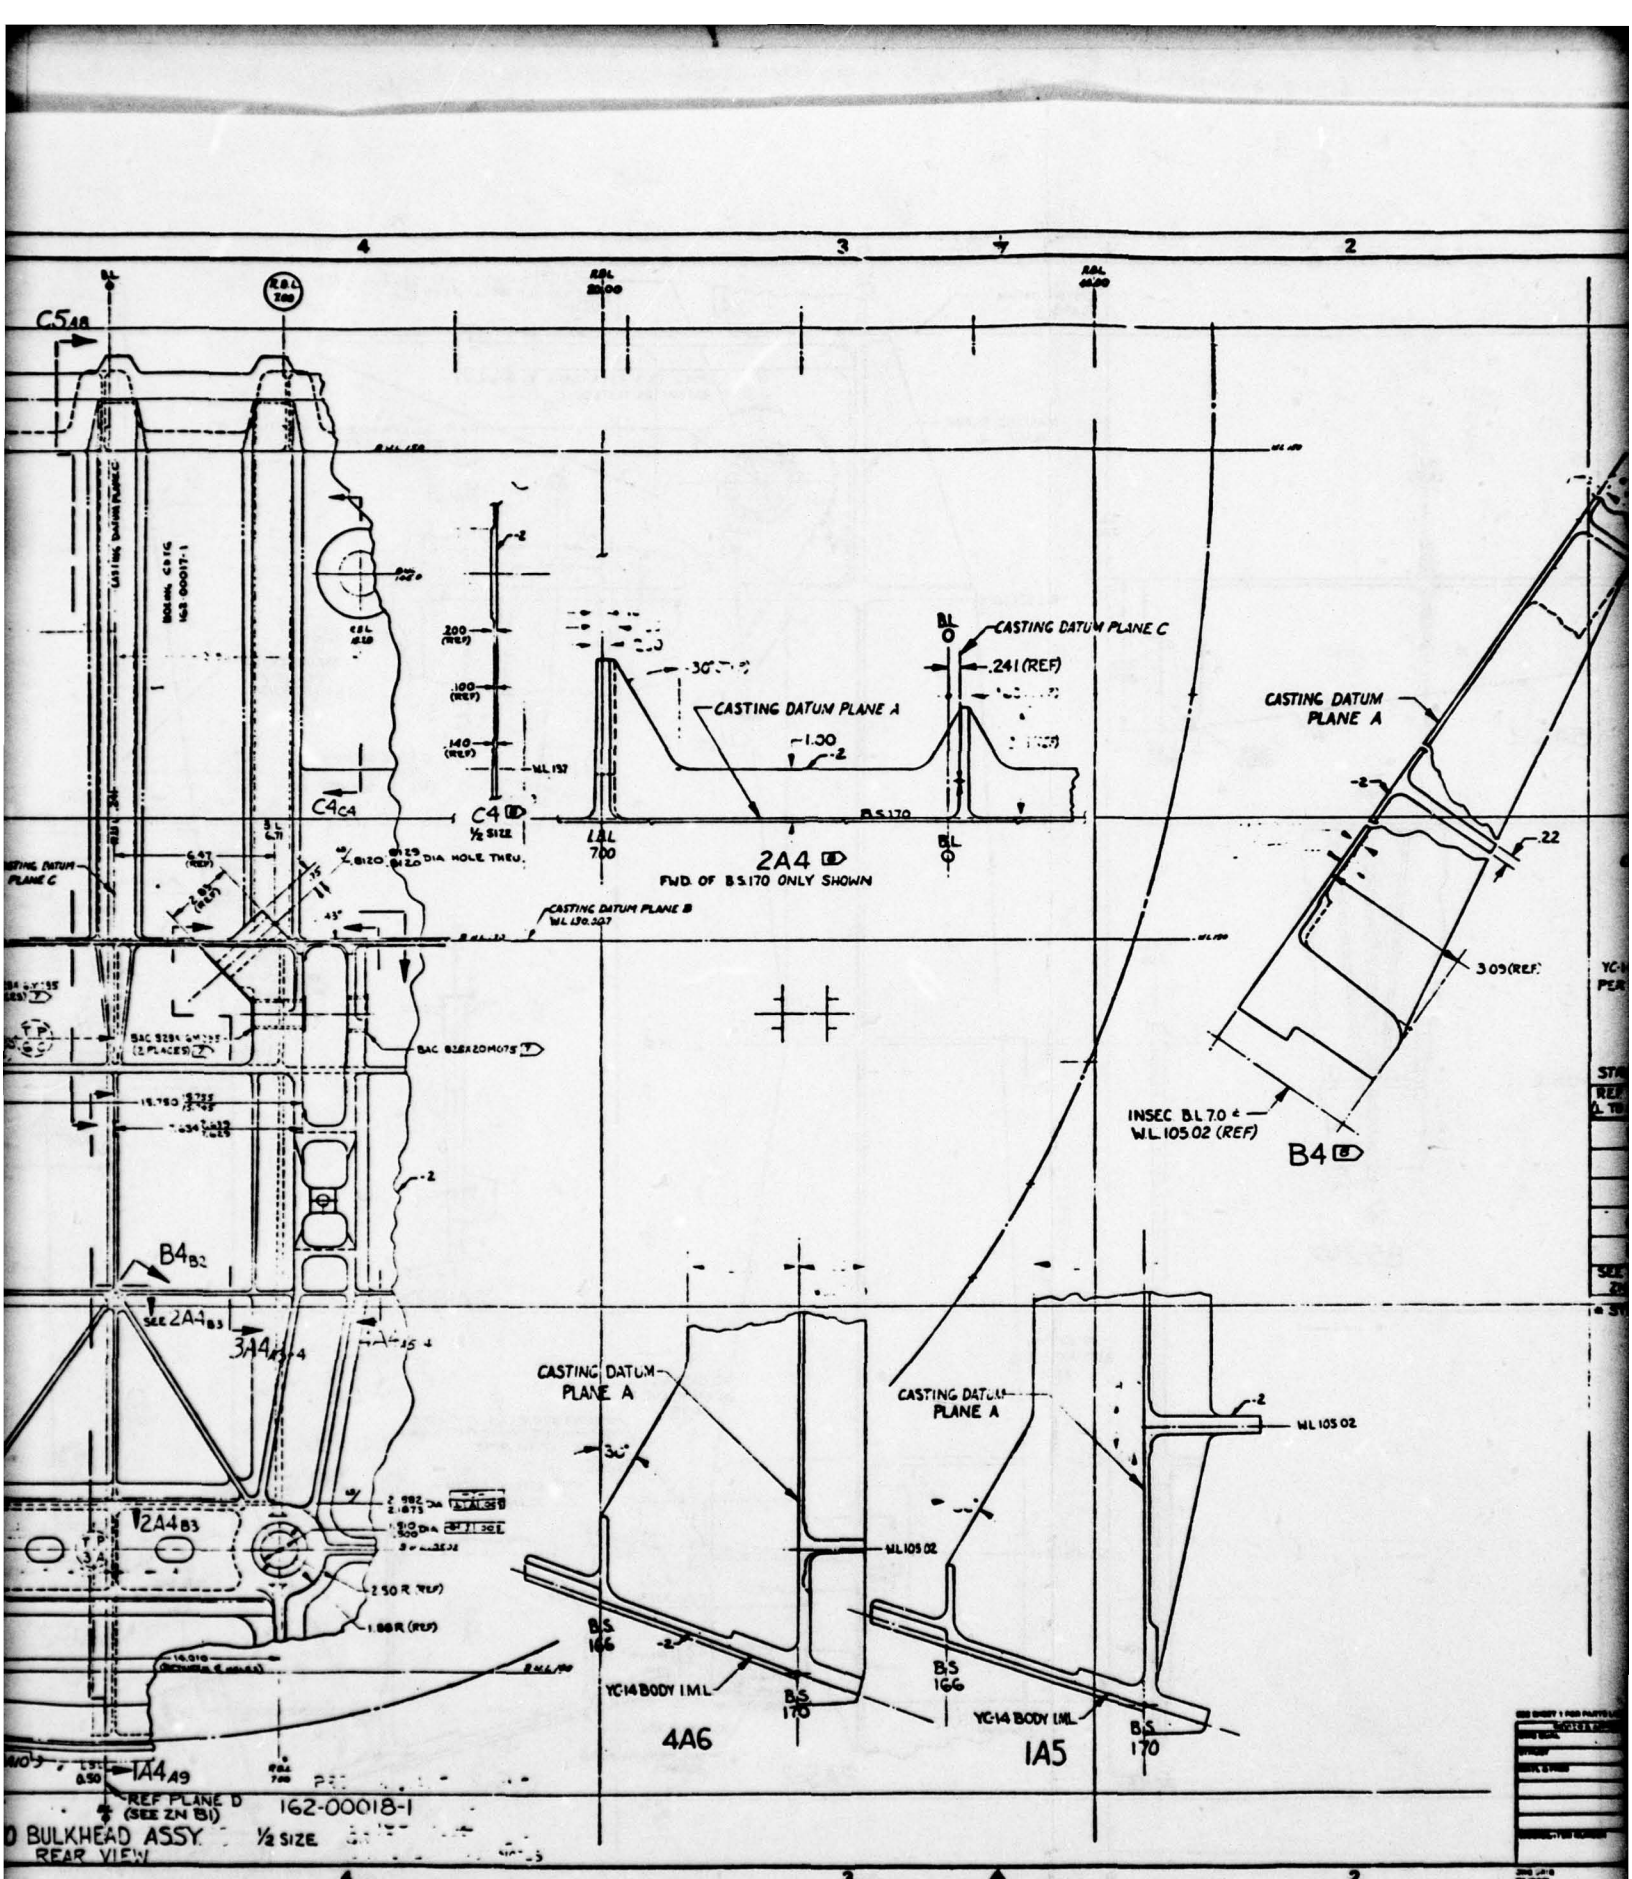
C5A8
C4C4
C4
½ SIZE
CASTING DATUM PLANE C
.241 (REF)
CASTING DATUM PLANE A
1.30
2A4
FWD. OF BS 170 ONLY SHOWN
CASTING DATUM PLANE B
WL 130.207
BAC B12AZ0M07
B4B2
SEE 2A4B3
3A4B4
2A4B3
2.50 R (REF)
1.88 R (REF)
TA4A9
REF PLANE D
(SEE ZN B1)
CASTING DATUM PLANE A
WL 105.02
BS 166
YC-14 BODY IML
BS 170
4A6
CASTING DATUM PLANE A
WL 105.02
BS 166
YC-14 BODY IML
BS 170
1A5
CASTING DATUM PLANE A
.22
3.09 (REF.)
INSEC BL 7.0 ℄
WL 105.02 (REF)
B4
162-00018-1
½ SIZE
REAR VIEW

4

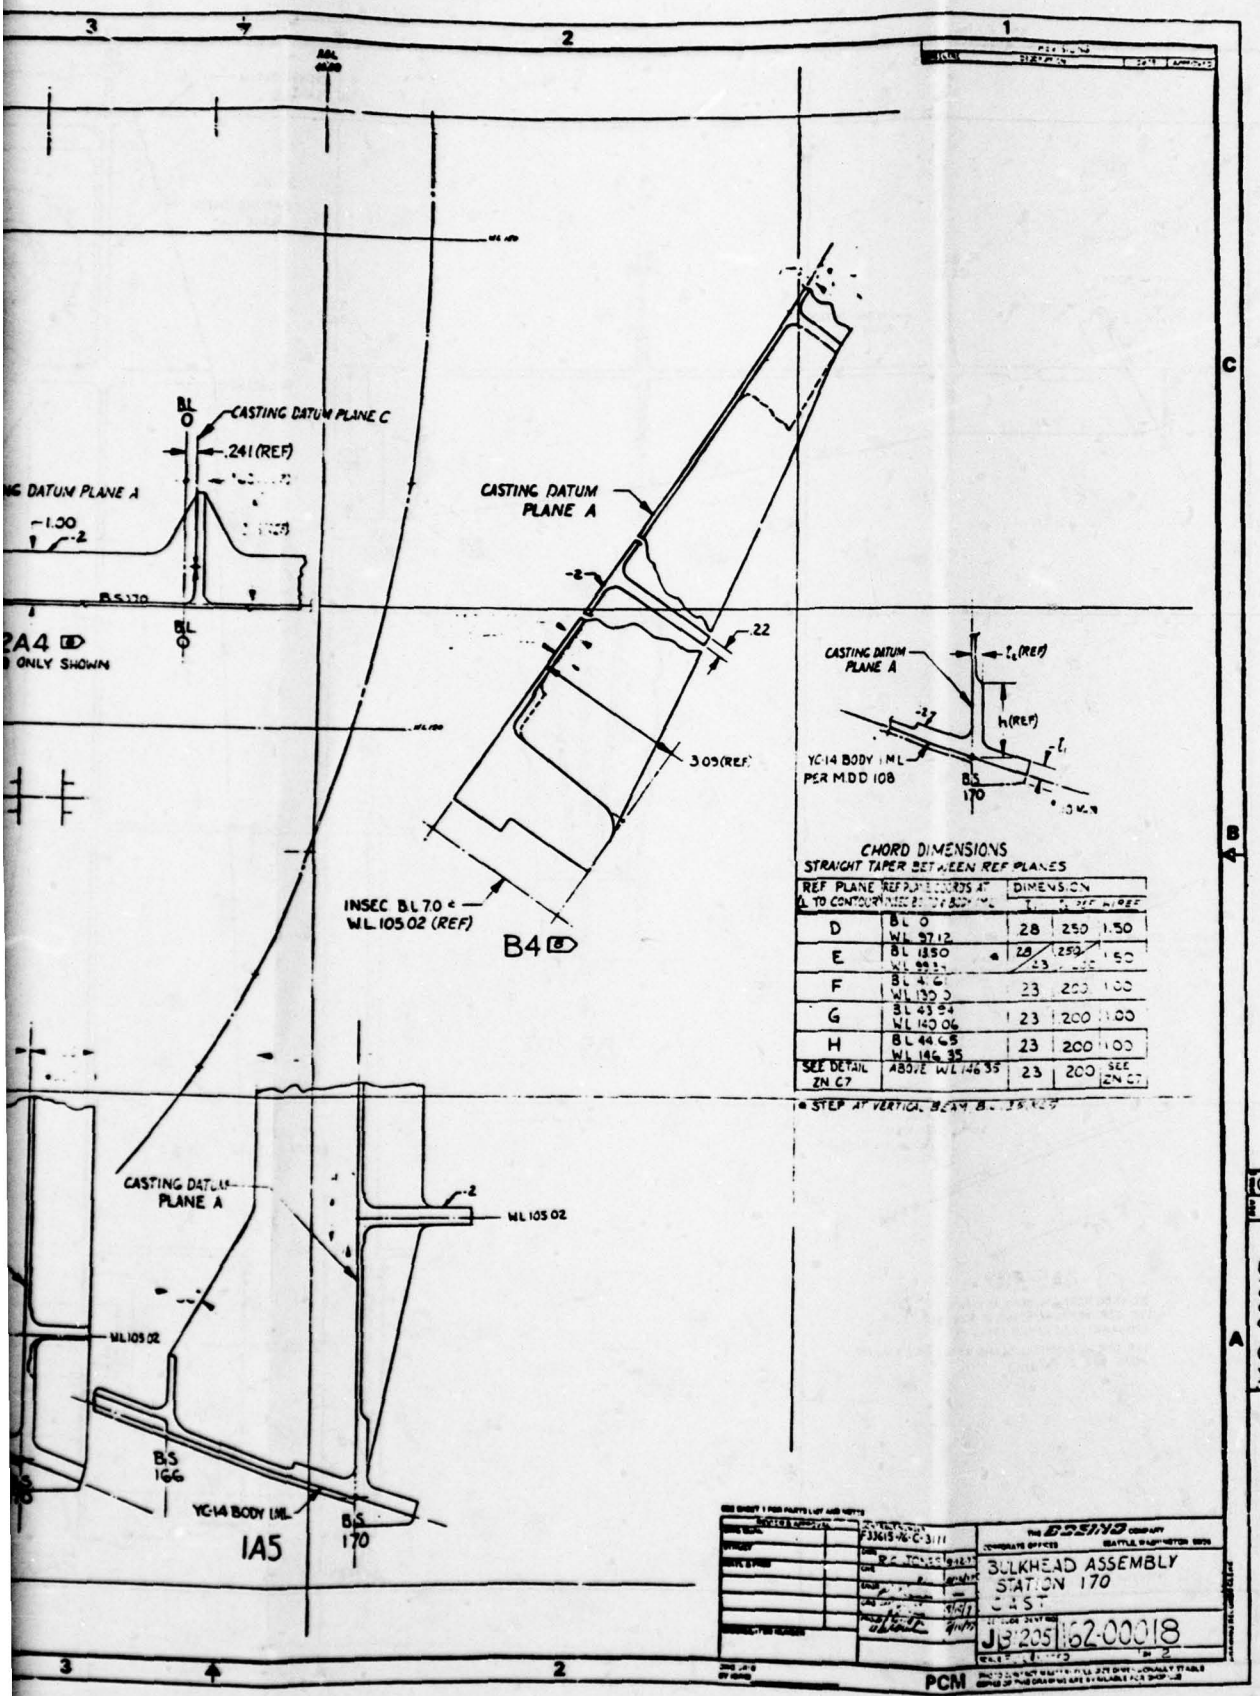
CASTING DATUM PLANE C
.241 (REF)
CASTING DATUM PLANE A
-1.30
-2
BS 170
2A4
ONLY SHOWN
CASTING DATUM PLANE A
-2
.22
.309 (REF)
INSEC BL 70 ℄
WL 105 02 (REF)
B4
CASTING DATUM PLANE A
t_c (REF)
h (REF)
YC-14 BODY LINE PER MDD 108
BS 170
CHORD DIMENSIONS
STRAIGHT TAPER BETWEEN REF PLANES
REF PLANE
REF POINT RECORDS AT ⊥ TO CONTOUR
DIMENSION
D
BL 0
WL 97.12
28
250
1.50
E
BL 1350
WL 99.30
28
23
250
F
BL 4 6
WL 130 0
23
200
1.00
G
BL 43 94
WL 140 06
23
200
1.00
H
BL 44 65
WL 146 35
23
200
1.00
SEE DETAIL ZN C7
ABOVE WL 146 35
23
200
SEE ZN C7
STEP AT VERTICAL BL
CASTING DATUM PLANE A
-2
WL 105 02
WL 105 02
BS 166
YC-14 BODY LINE
BS 170
1A5
THE BOEING COMPANY
SEATTLE, WASHINGTON
BULKHEAD ASSEMBLY
STATION 170
CAST
JB 205
162-00018
PCM
162-00018
185-00018

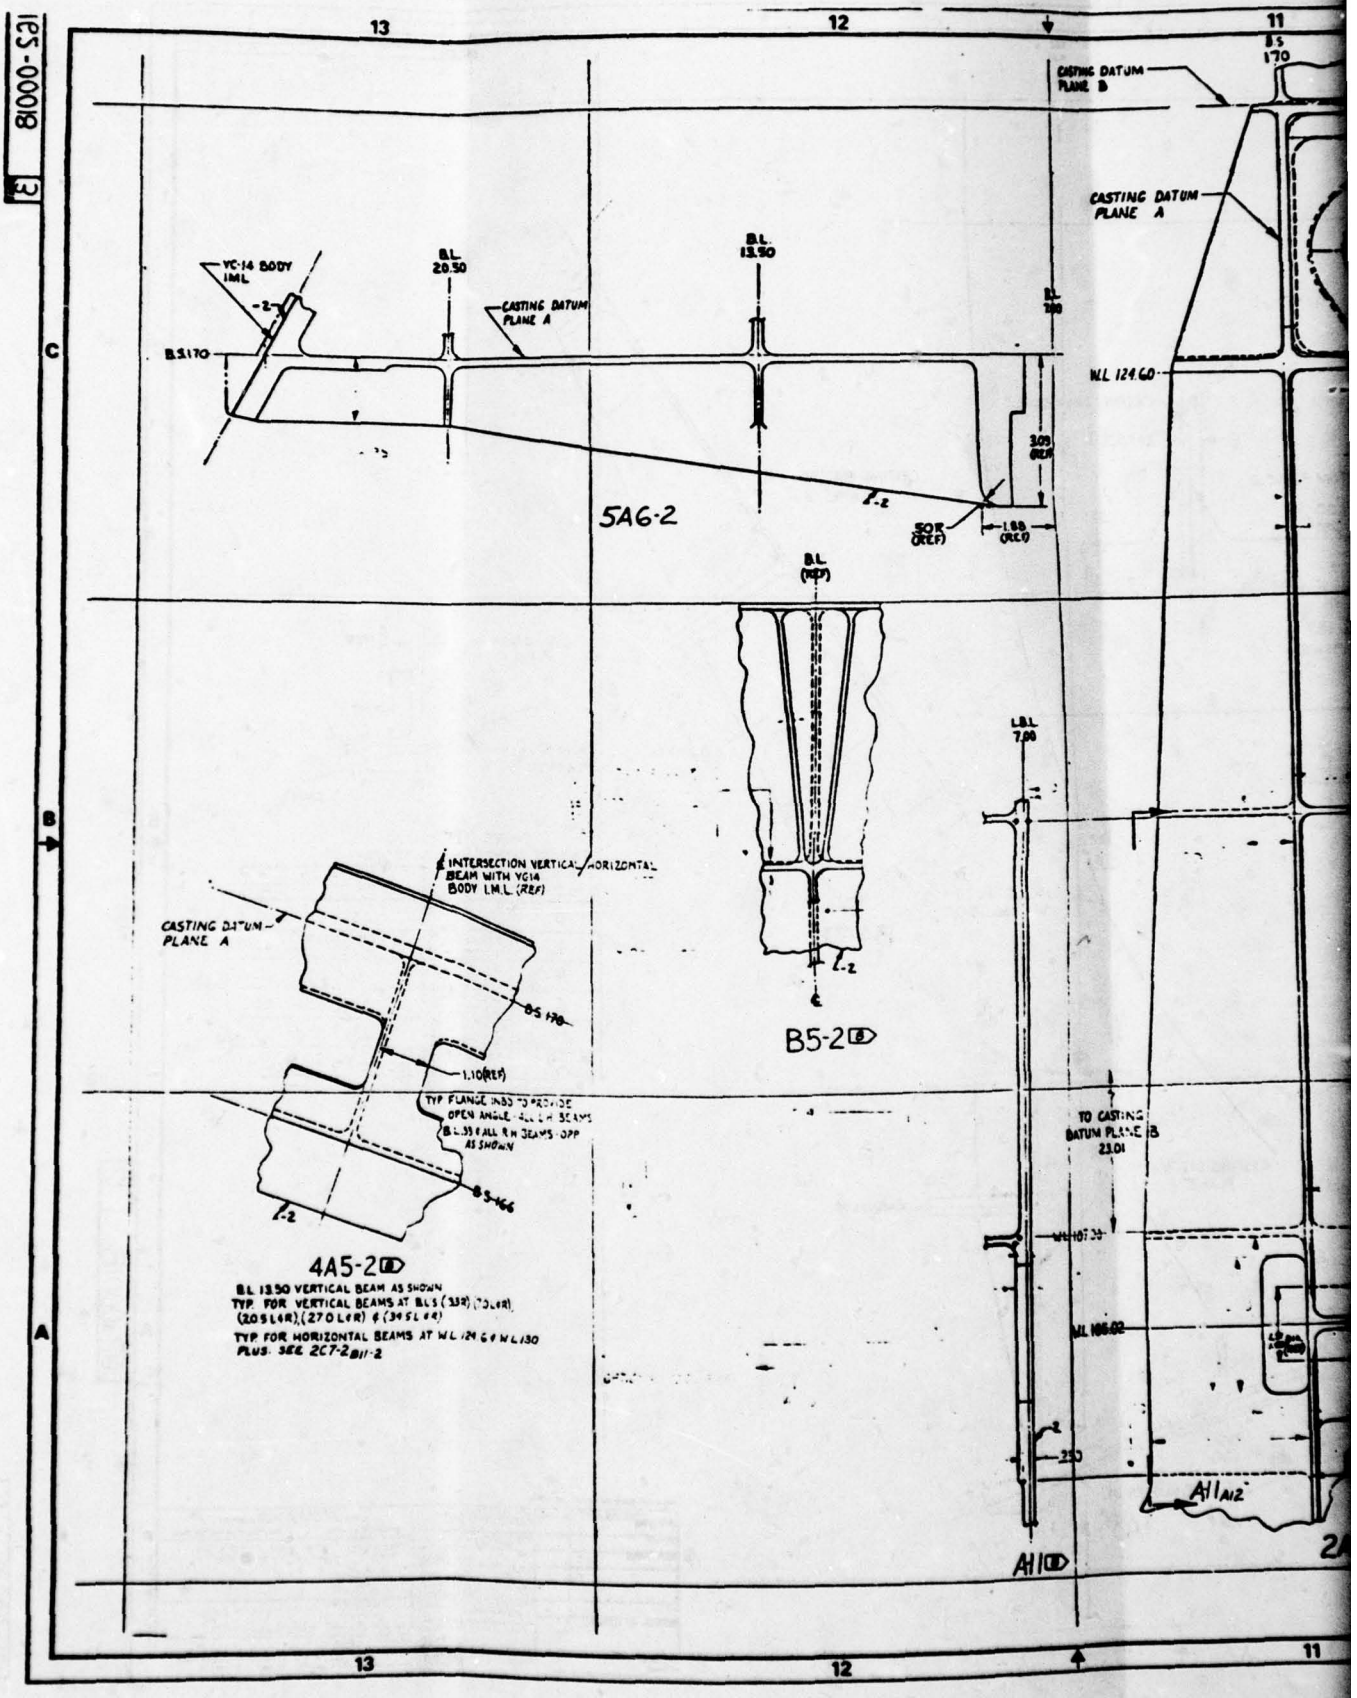
13
12
11
B.S 170
CASTING DATUM PLANE B
CASTING DATUM PLANE A
YC-14 BODY LM.L
B.L 20.50
B.L 13.50
B.S 170
W.L 124.60
5A6-2
SOR (REF)
B.L (TYP)
B5-2
LBL 7.00
CASTING DATUM PLANE A
INTERSECTION VERTICAL/HORIZONTAL BEAM WITH YG14 BODY L.M.L (REF)
B.S 170
1.10 (REF)
TYP FLANGE INBD TO PROVIDE OPEN ANGLE
B.S 166
4A5-2
B.L 13.50 VERTICAL BEAM AS SHOWN
TYP. FOR VERTICAL BEAMS AT B.L.S (33R) (7.5 L&R) (20.5 L&R), (27.0 L&R) & (34 5 L&R)
TYP FOR HORIZONTAL BEAMS AT W.L 124.6 & W.L 130
PLUS. SEE 2C7-2 B11-2
TO CASTING DATUM PLANE B 23.01
W.L 107.30
W.L 106.02
A11 A12
A11
A
B
C

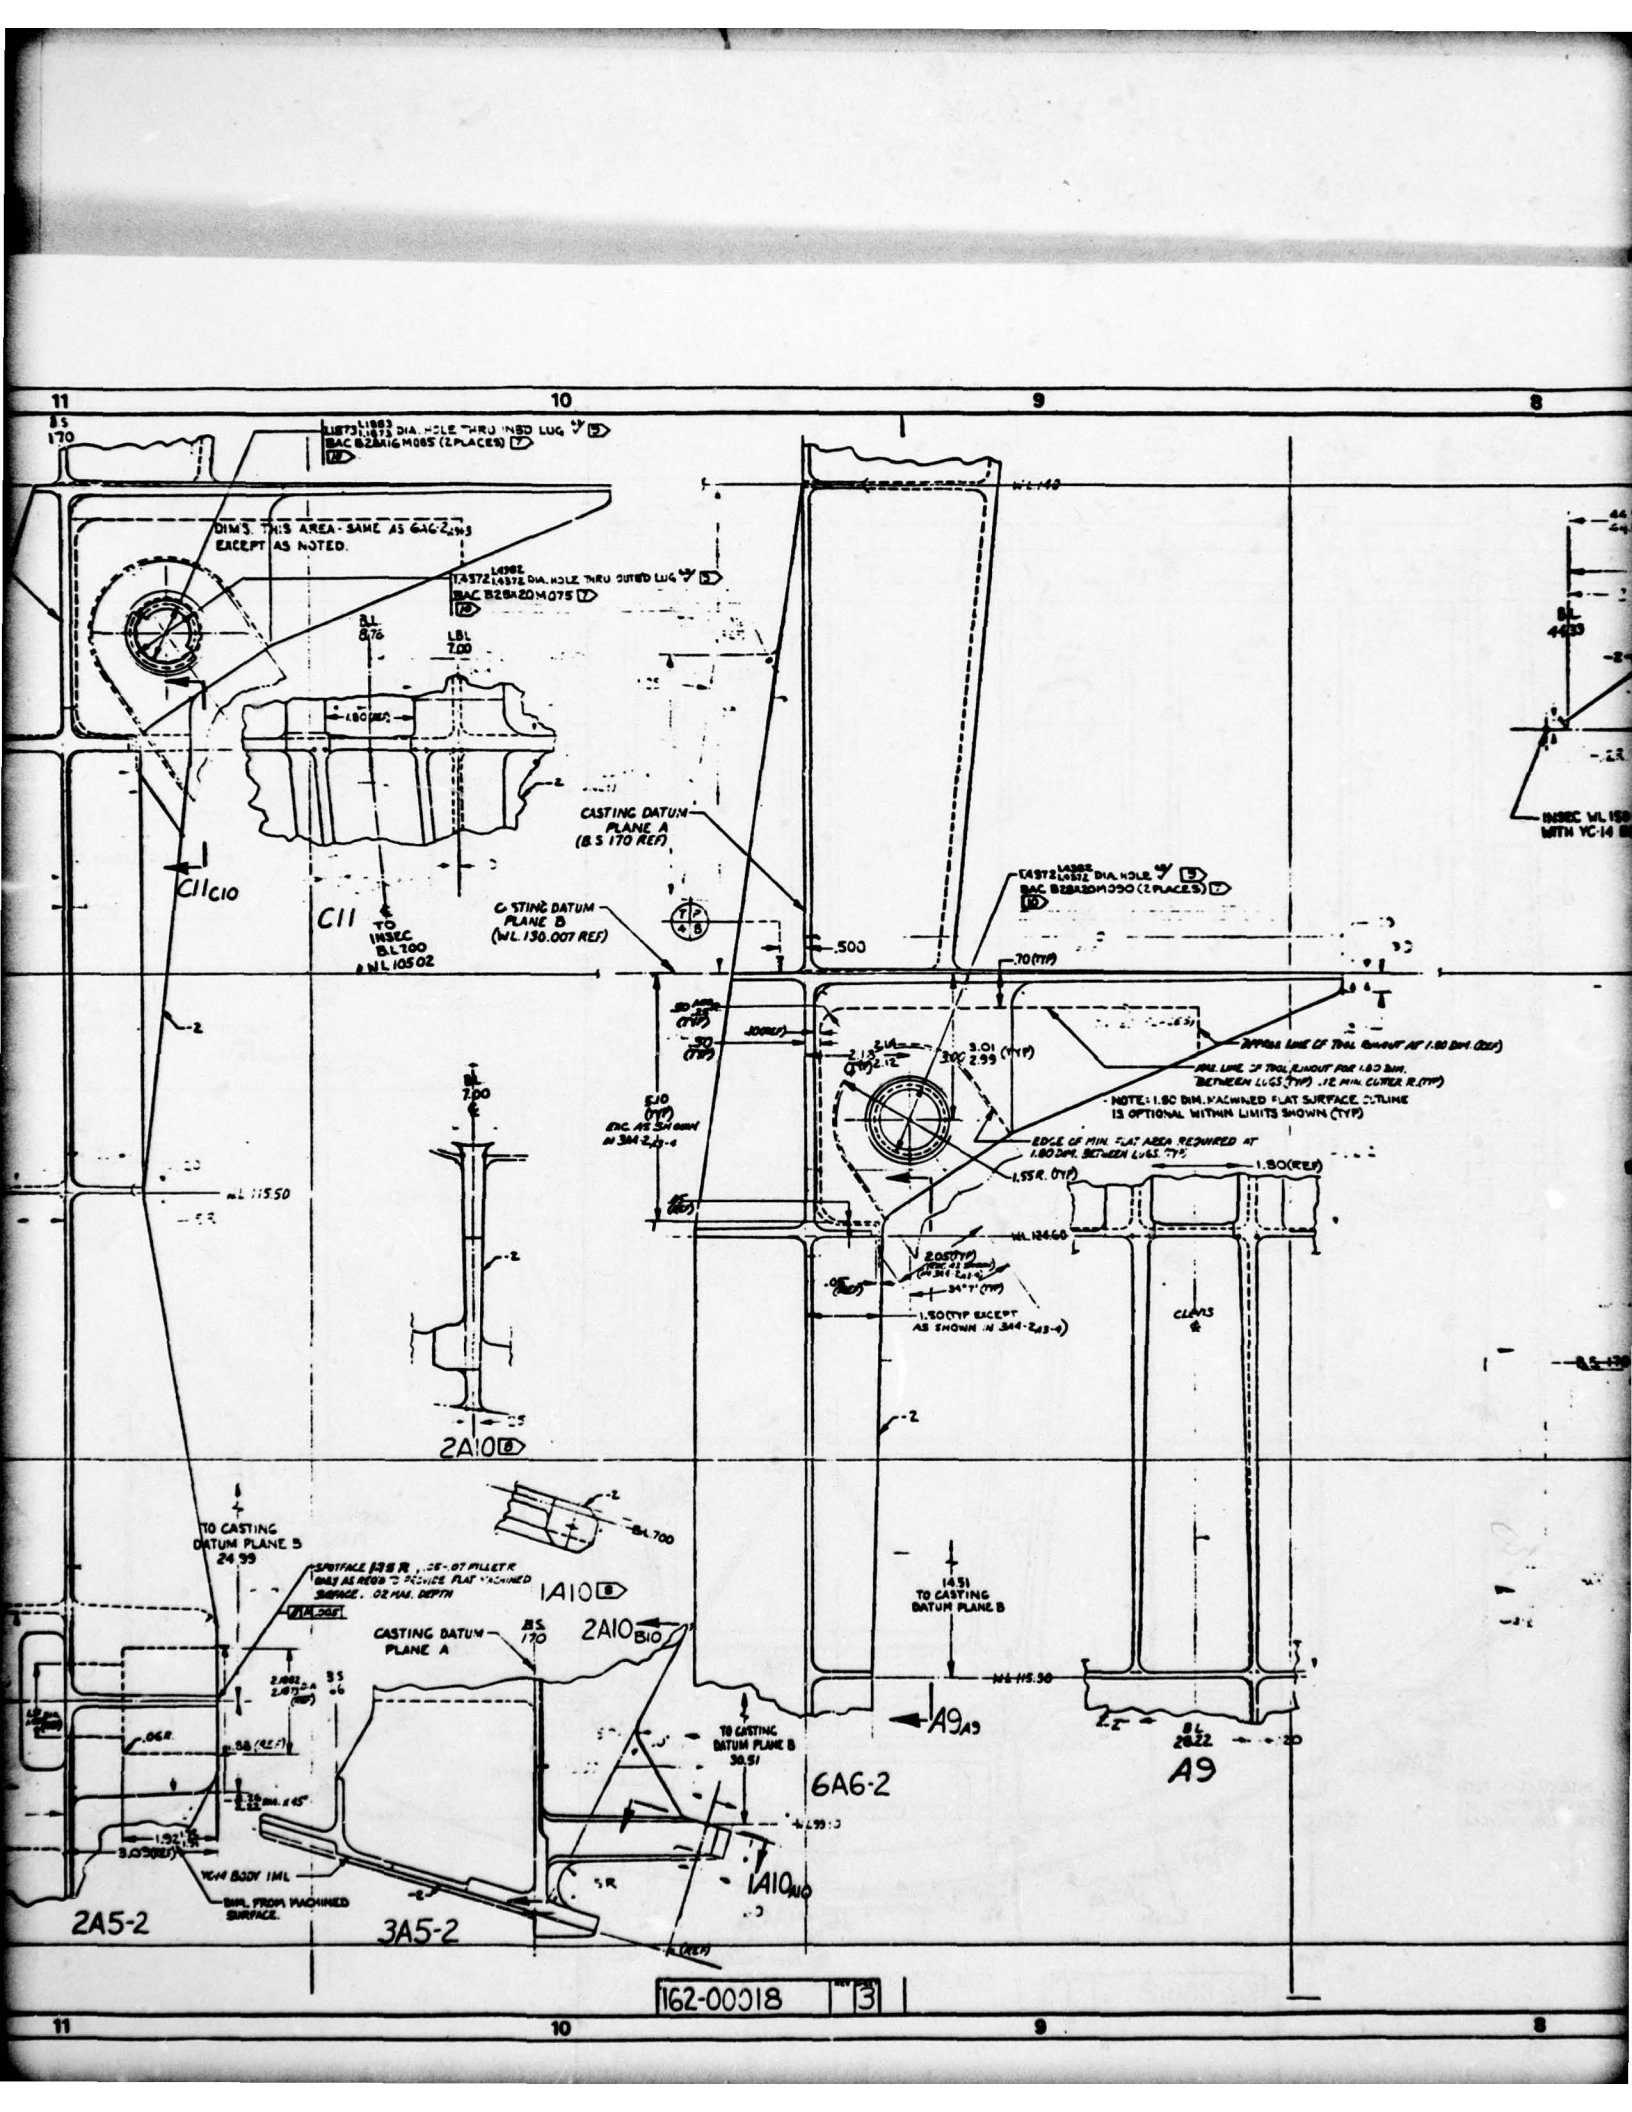
11
10
9
8
DIM'S THIS AREA - SAME AS 6A6-2 EXCEPT AS NOTED.
CASTING DATUM PLANE A (B.S 170 REF)
CASTING DATUM PLANE B (WL 130.007 REF)
TO CASTING DATUM PLANE B 24.99
TO CASTING DATUM PLANE B 30.51
14.51 TO CASTING DATUM PLANE B
CASTING DATUM PLANE A
2A10
1A10
2A10
1A10
6A6-2
A9
2A5-2
3A5-2
NOTE: 1.80 DIM. MACHINED FLAT SURFACE OUTLINE IS OPTIONAL WITHIN LIMITS SHOWN (TYP)
1.80(REF)
1.50(TYP EXCEPT AS SHOWN IN 344-243-4)
.500
.70(TYP)
WL 115.50
WL 124.60
WL 140
TO INSEC. B.L 7.00 & WL 105.02
INSEC WL 150 WITH YC-14
162-00018
3

7
6
5
LBL 38.00
LBL 28.00
LBL 21.00
LBL 14.00
C9-2
ROTATED
C TAB (TYP)
IC8-2
ROTATED
SLANTED BEAM TABBED FU
B.S.166
YC-14 BODY IML
B.S.130
BL 29.04
LBL 28.00 (38 OPP)
BL 25.75
21.240
BAC B28K20
BAC B28K20 MOSC (2 PLACES)
BL 32.08
BL 34.50
CORRUGATION
BL 28.22
CORR. @WL 130
BL 20.50
CORRUGATION
BL 13.50
CORRUGATION
.12 (REF)
B7-2
162-00018
REV 3
7
6
5

3

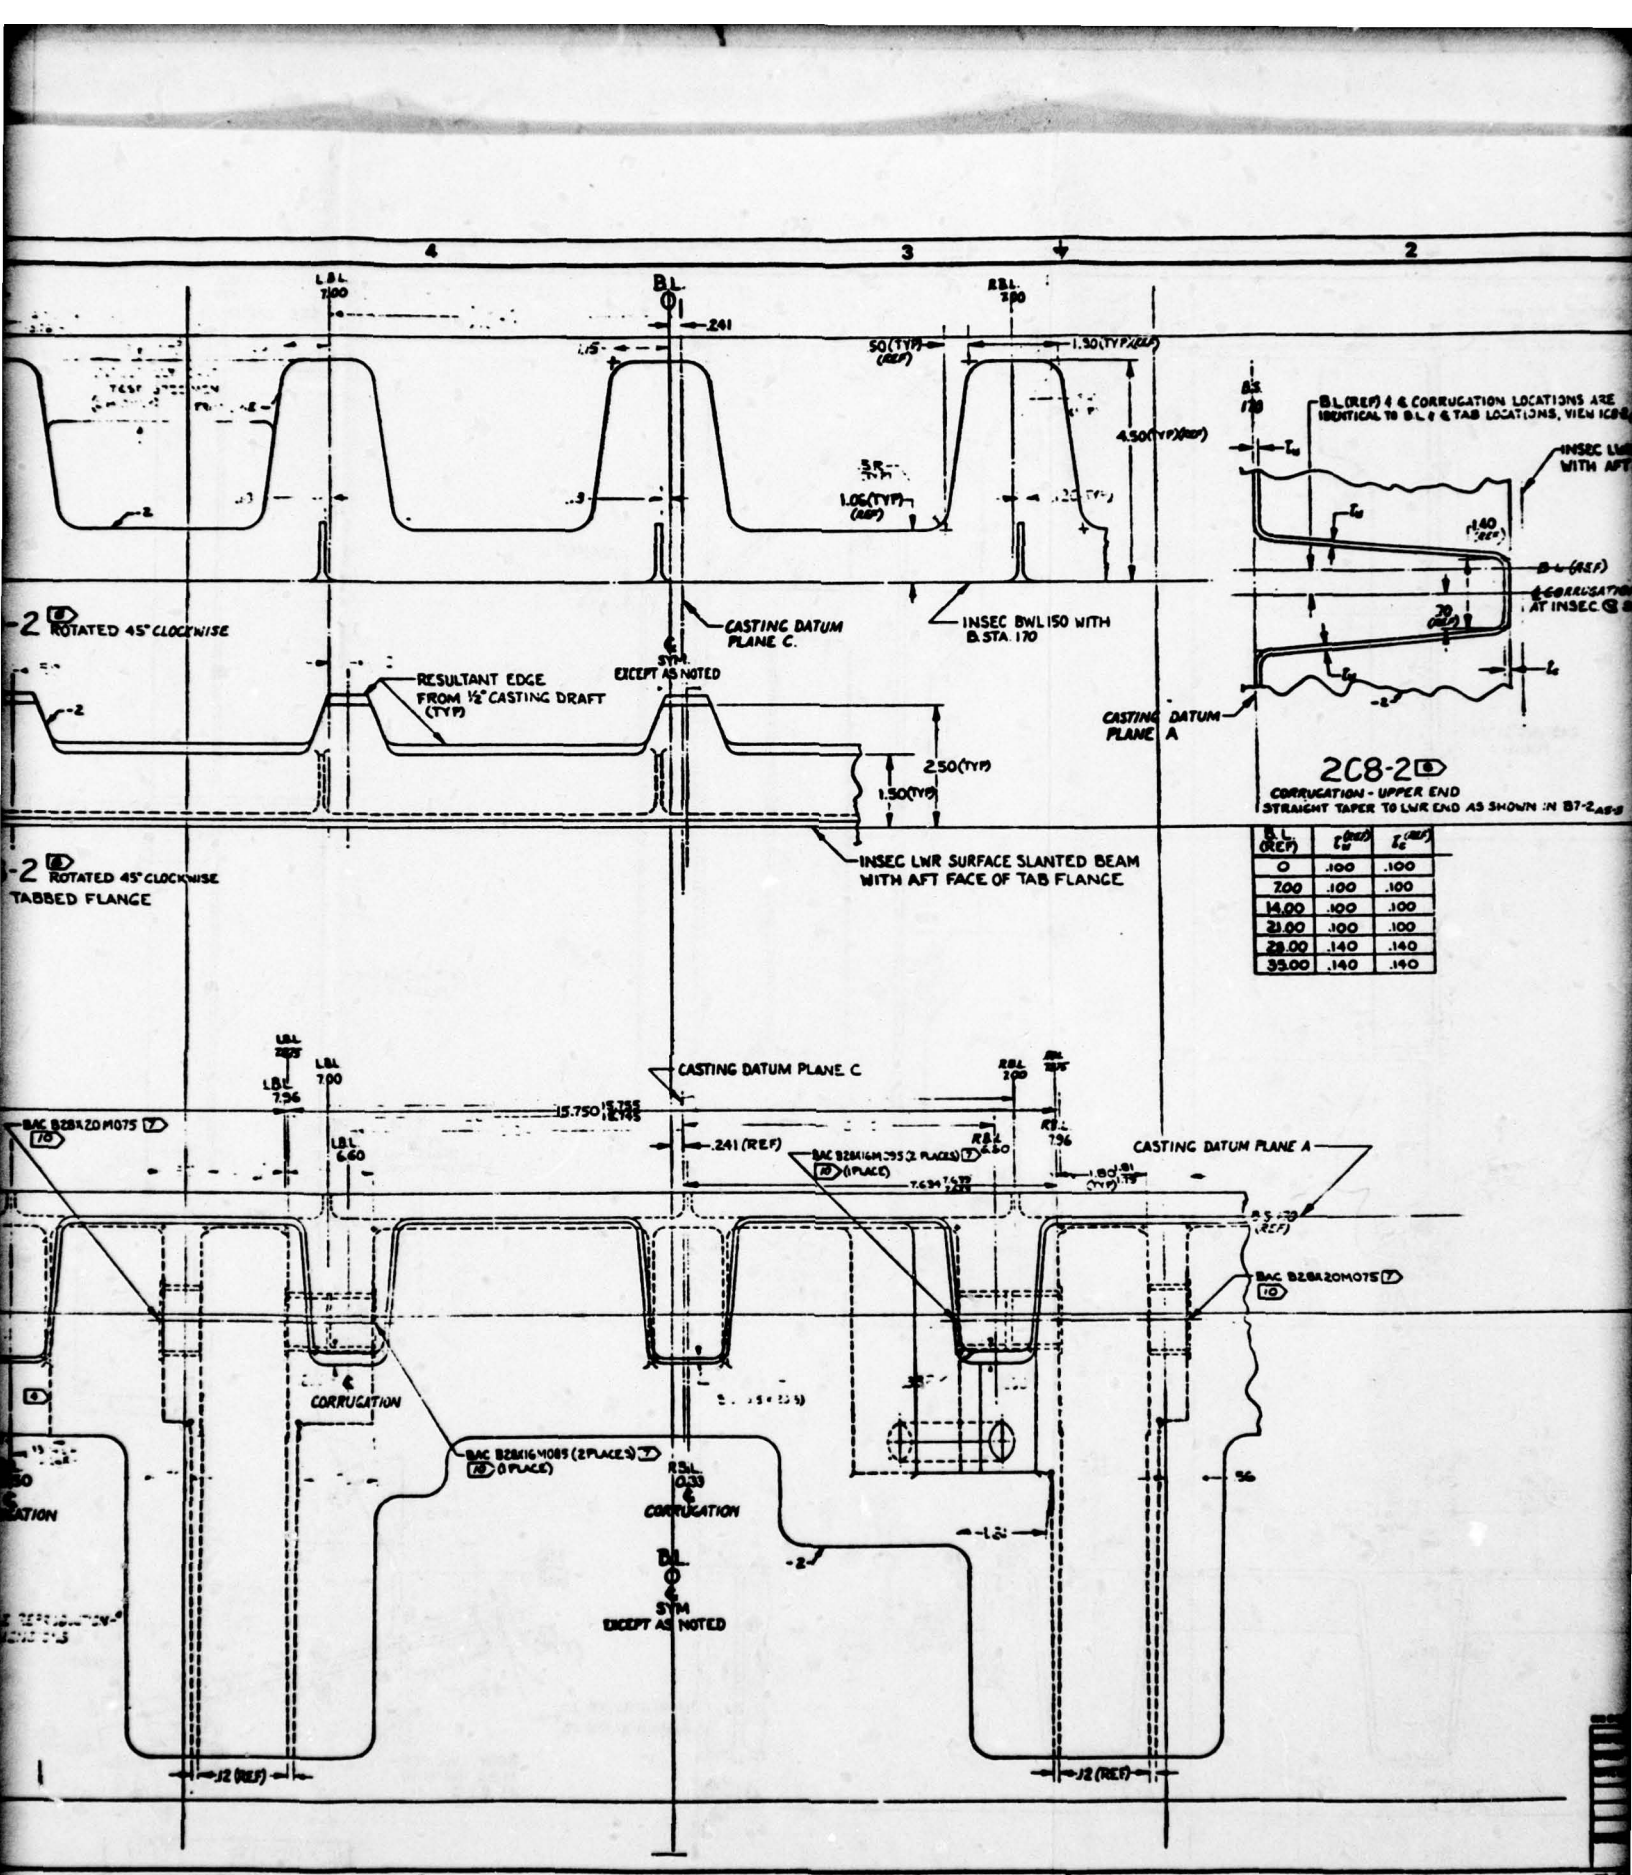
4
3
2
B.L.
0
L.B.L. 7.00
R.B.L. 7.00
.241
.50 (TYP) (REF)
1.50 (TYP) (REF)
4.50 (TYP) (REF)
1.06 (TYP) (REF)
CASTING DATUM PLANE C.
INSEC BWL 150 WITH B. STA. 170
RESULTANT EDGE FROM 1/2° CASTING DRAFT (TYP)
℄ SYM EXCEPT AS NOTED
2.50 (TYP)
1.50 (TYP)
INSEC LWR SURFACE SLANTED BEAM WITH AFT FACE OF TAB FLANGE
-2 ROTATED 45° CLOCKWISE
-2 ROTATED 45° CLOCKWISE TABBED FLANGE
B.L. (REF) & CORRUGATION LOCATIONS ARE IDENTICAL TO B.L. & TAB LOCATIONS, VIEW 208-2
INSEC LWR WITH AFT
CASTING DATUM PLANE A
208-2
CORRUGATION - UPPER END
STRAIGHT TAPER TO LWR END AS SHOWN IN B7-2
B.L. (REF) | t_{cu} (REF) | t_{cl} (REF)
0 | .100 | .100
7.00 | .100 | .100
14.00 | .100 | .100
21.00 | .100 | .100
28.00 | .140 | .140
35.00 | .140 | .140
CASTING DATUM PLANE C
CASTING DATUM PLANE A
L.B.L. 7.96
L.B.L. 6.60
R.B.L. 6.50
R.B.L. 7.96
15.750
.241 (REF)
BAC B28A20M075 (7) (10)
BAC B28A16M095 (2 PLACES) (7) (10) (1 PLACE)
BAC B28A16M085 (2 PLACES) (7) (10) (1 PLACE)
CORRUGATION
R.B.L. 0.39
.12 (REF)
-2
SYM EXCEPT AS NOTED

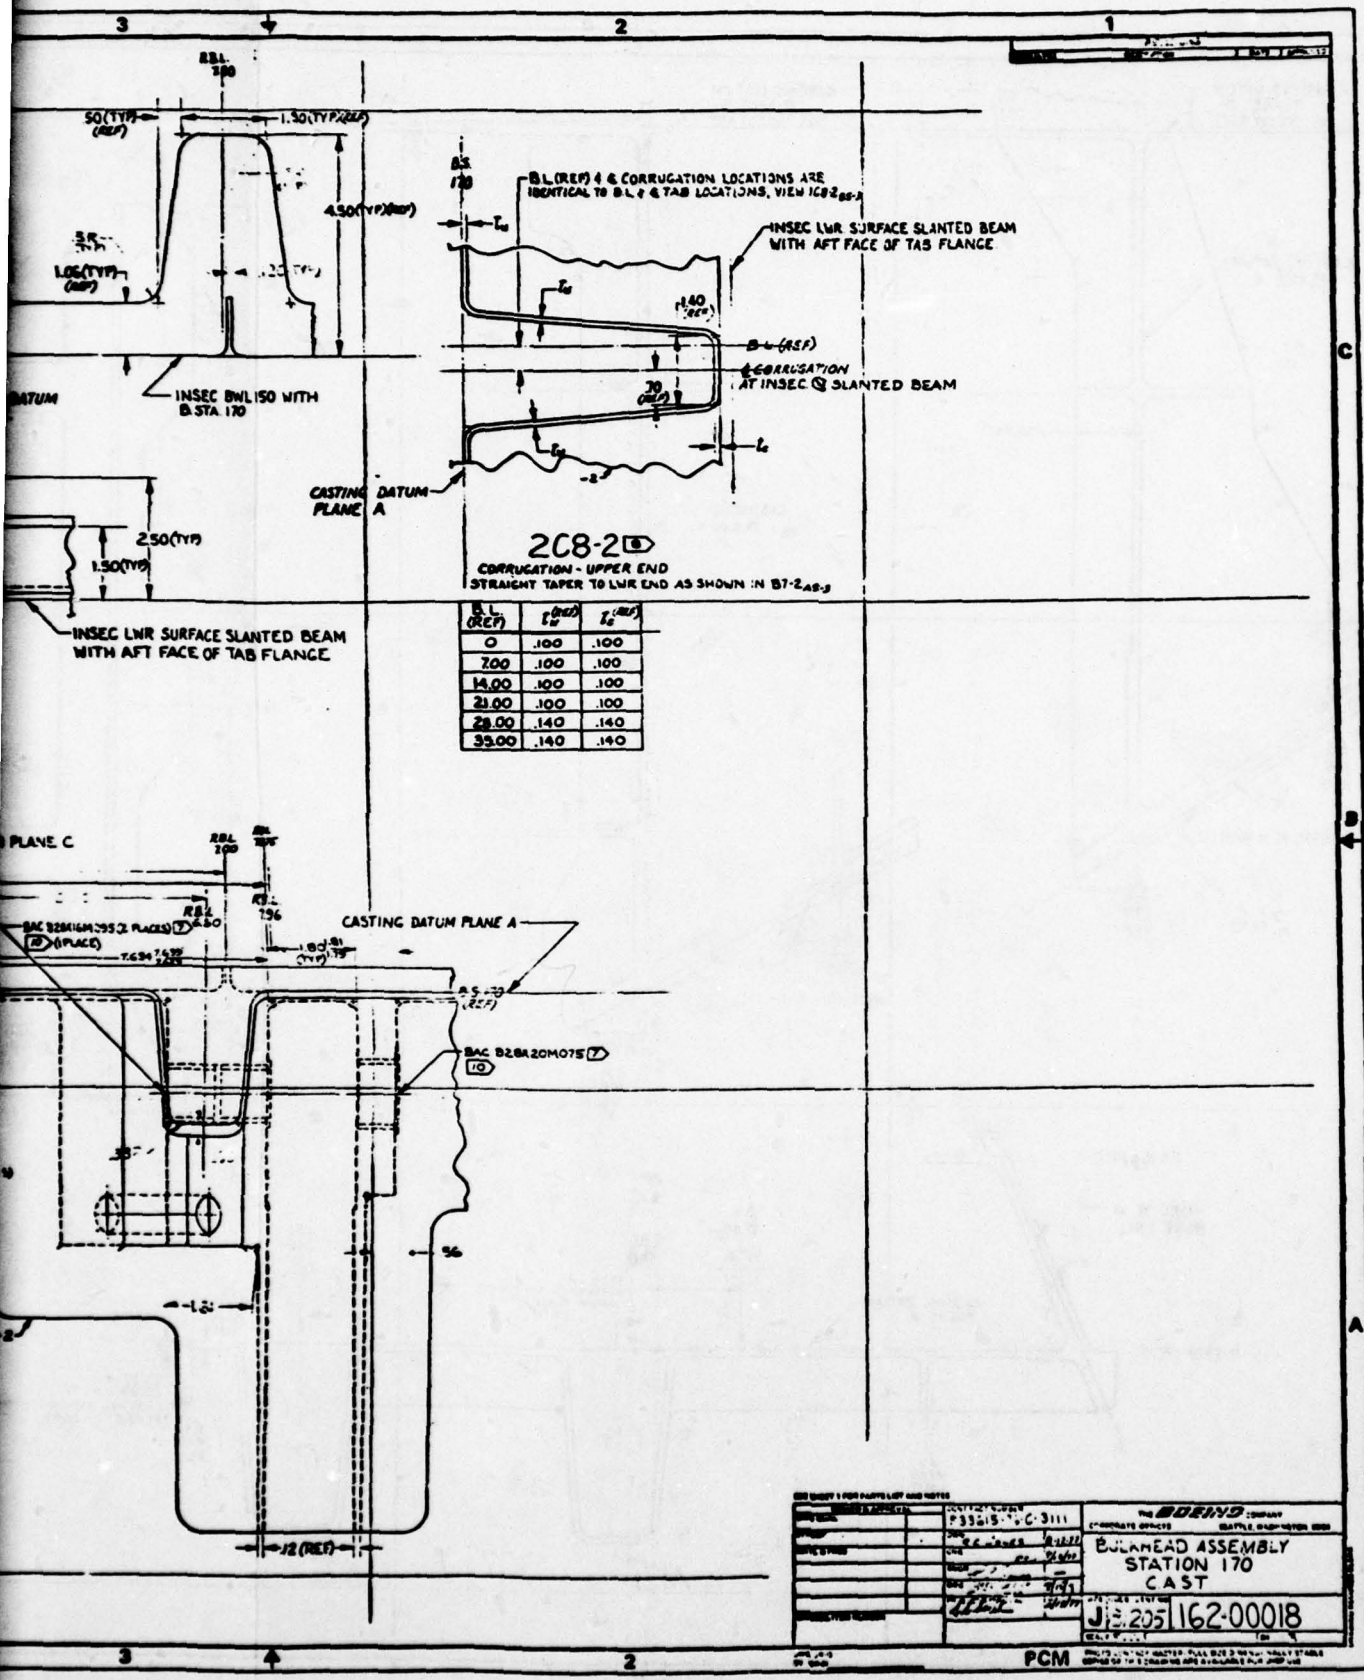

B.L. (REF)	t_w (REF)	t_c (REF)
0	.100	.100
7.00	.100	.100
14.00	.100	.100
21.00	.100	.100
28.00	.140	.140
35.00	.140	.140

	P33215-*-C-3111	THE BOEING COMPANY	
		BULKHEAD ASSEMBLY STATION 170 CAST	
		J 5.205	162-00018

PCM

162-00018 [3]

IPS-00018 [2]

16

81000-S21
9
8
7
C
B
A
9
8
7

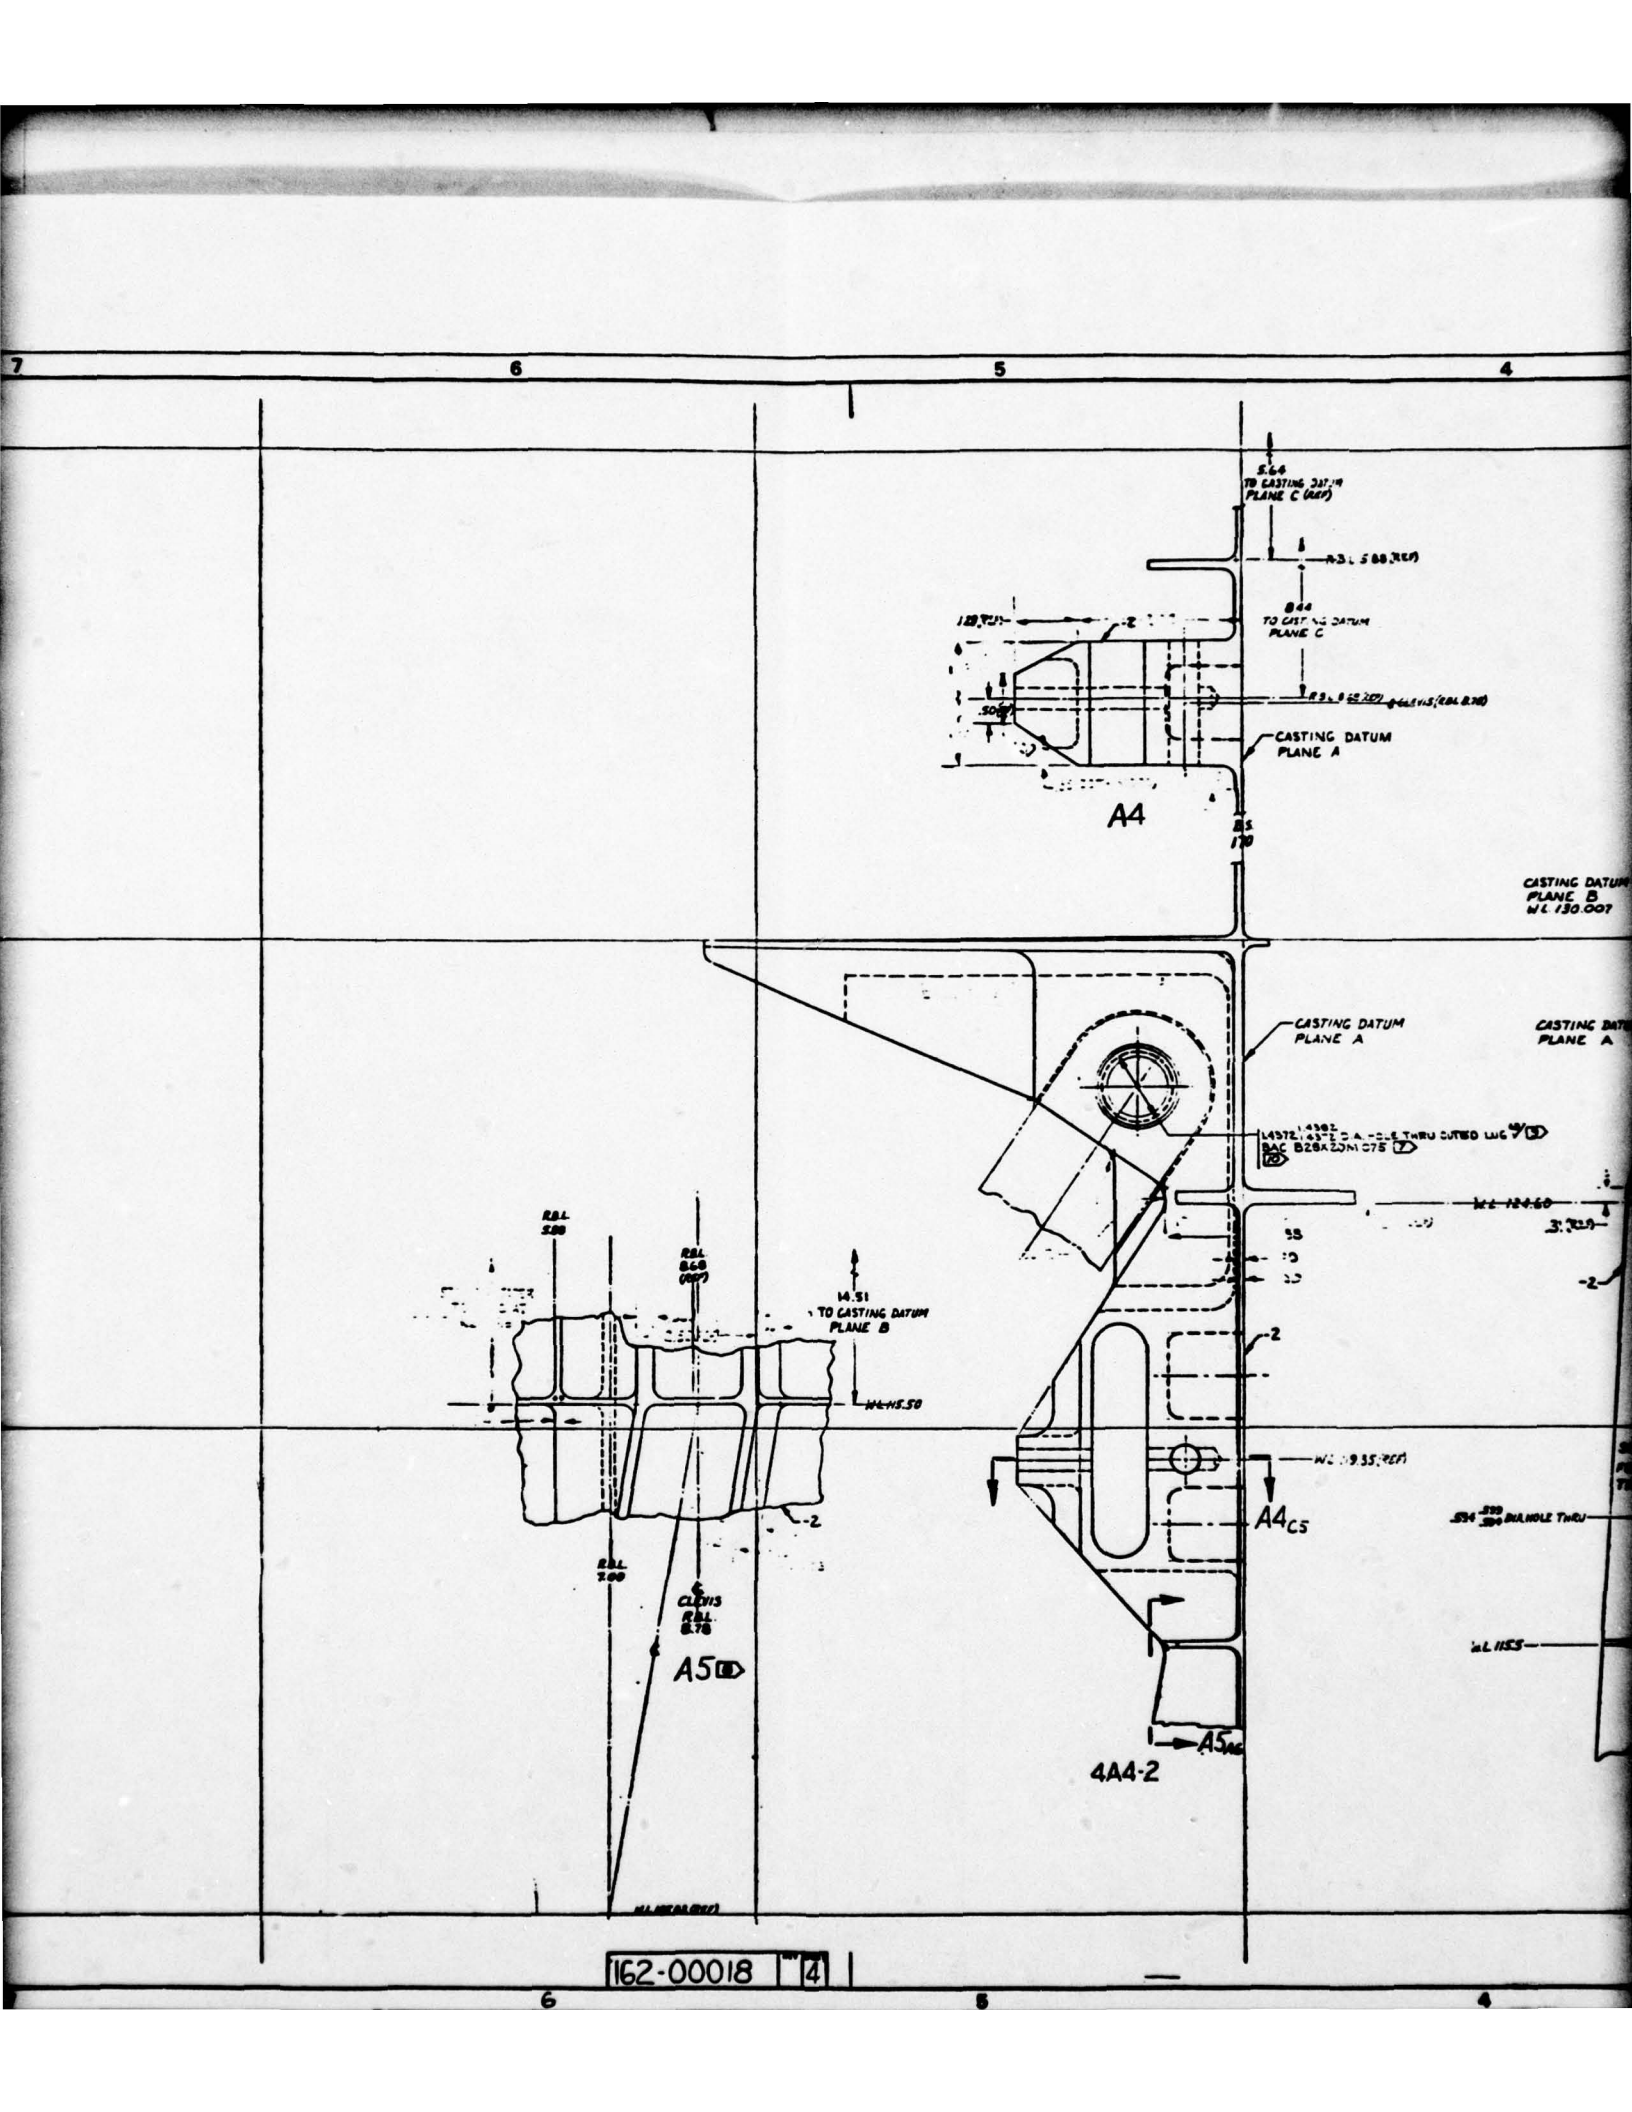
7
6
5
4
CASTING DATUM PLANE A
A4
CASTING DATUM PLANE B
CASTING DATUM PLANE A
CASTING DATUM PLANE A
A4C5
A5
A5
4A4-2
162-00018
4

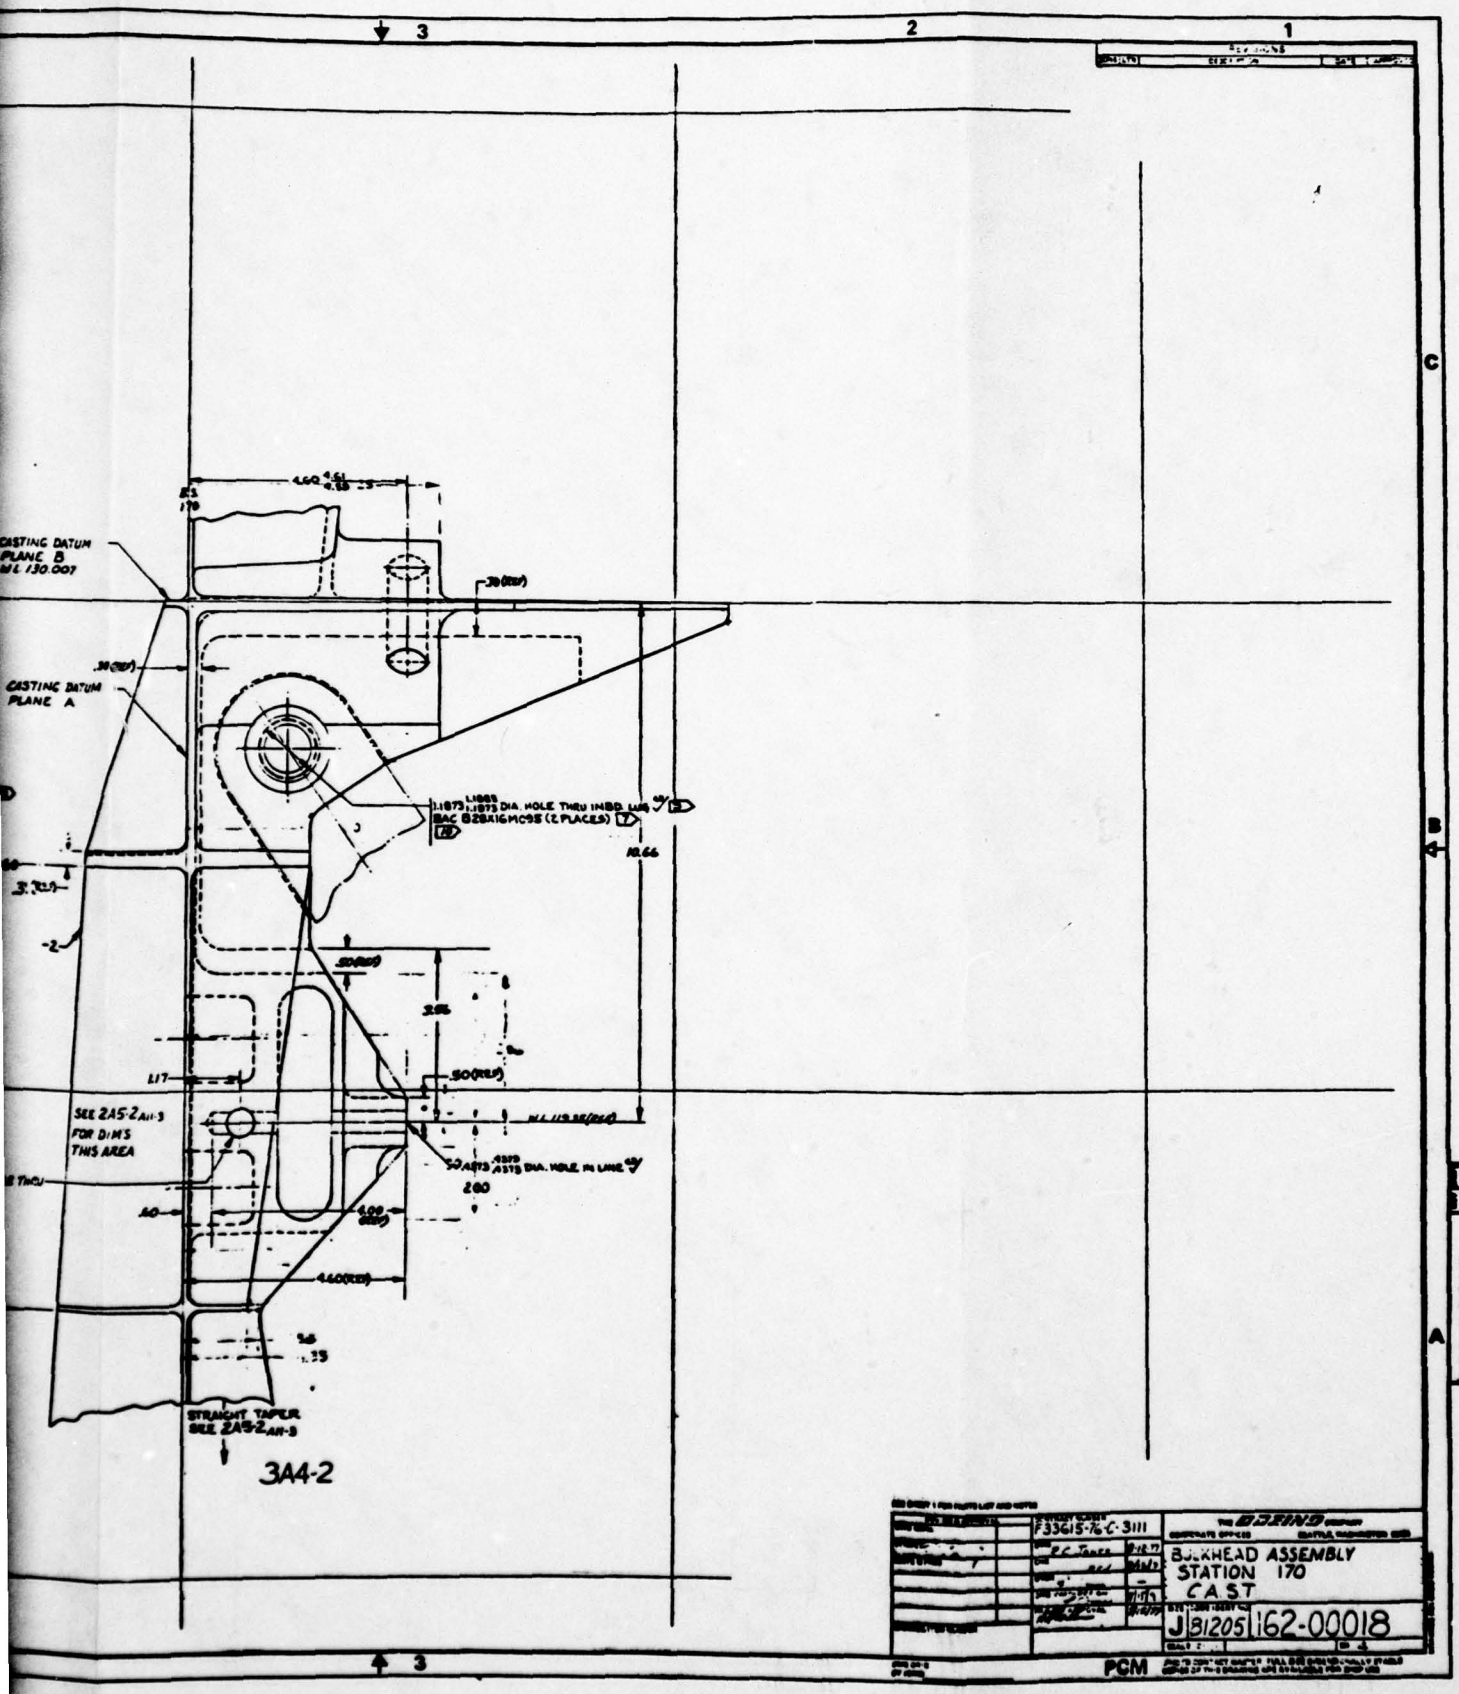
3
2
1
C
B
A
CASTING DATUM PLANE B
CASTING DATUM PLANE A
SEE 2A5-2 ALL-3 FOR DIMS THIS AREA
STRAIGHT TAPER SEE 2A5-2 ALL-3
3A4-2
BULKHEAD ASSEMBLY
STATION 170
CAST
J81205 162-00018
F33615-76-C-3111
PCM
162-00018
17

5. BASELINE COMPONENT DATA

a. Initial Baseline Component Data

The initial baseline cost data were derived during Phase I, Preliminary Design. The first unit YC-14 bulkhead total cost was estimated to be $122,000 and the projected unit cost of the bulkhead, based on a 300-airplane production run, was $10,900. These costs were derived primarily from actual records and are for the built-up baseline component bulkhead prior to release of the updated baseline data.

The initial baseline component weight was 184.6 lb. This weight was the actual weight of the YC-14 baseline component bulkhead and did not reflect a reduction for non-optimum prototype structures.

b. Updated Baseline Component Data

A baseline component revision was released September 30, 1977. The revised baseline component includes the original YC-14 bulkhead components plus that portion of the slanted beam assembly at WL 150 between LBL 41.0 and RBL 41.0. The updated cost summary is shown in figure 2, giving both the first unit cost and the projected unit cost based on a 300-airplane production run. The $12,894 figure replaces the $10,900 previously used for a cost comparison of the cast concept versus the baseline component.

The revised baseline component weight is 187.6 lb. This weight is for the YC-14 component components plus the WL 150 slanted beam between LBL 41.0 and RBL 41.0, and also includes the deletion of non-optimum weight items that would not be required on a production (YC-14) bulkhead.

	No. 1 A/P cost	300 A/P cost
Raw material	$ 1,228	$ 384,000
Labor:		
Detail tools	45,450	302,577
Assembly tools	55,325	366,345
Detail fabrication	45,250	1,701,120
Sub-assembly	9,750	743,505
Section installation	--	247,680
Total	$157,003	$3,745,227
Cost per unit	$157,003	$ 12,484

Figure 2. Conventionally Fabricated Station 170 Bulkhead Costs Updated Baseline Component

SECTION III

ANALYSIS

1. STATIC STRENGTH ANALYSIS

The YC-14 design loads were used to structurally size the cast bulkhead and transition structure. A finite element computer model was used to calculate the internal loads. The exploded computer model geometry of the cast bulkhead and transition structure (fig. 3) is shown on figures 4 and 5. Detailed sections of the computer model showing nodes, rods, beams, and plates can be seen in figures 6 through 14. Loads were applied at specific nodes to simulate landing gear loads and loads due to a jammed landing gear door actuator. All nodes in the computer model are fixed at station 230.

Detailed stress analysis of major critical components includes:

- o Lug analysis of BL 28 (Figure 15)
- o Critical webs (Figures 16 through 20)
- o Stiffener at BL 28 (Figures 21 through 27)
- o Horizontal beam at WL 150 (Figures 28 through 30)
- o Bulkhead perimeter chord (Figures 31 through 33)
- o Backup structure for landing gear door actuator (Figures 34 and 35)
- o Lug backup structure at BL 8.7 (Figure 36)

a. Summary of Margins of Safety

The following summarizes the margins of safety of the critical components. The least margins of safety were found for the lug at BL 28 and for the perimeter beam at WL 150. The lug exhibits a positive 9% margin of safety for the maximum tensile force and the perimeter beam also shows a 9% positive margin of safety for combined bending and axial loads.

Critical Component	Fig. No.	M.S.
Critical lug at BL 28		
Shear-Bearing	15	+0.13
Tension	15	+0.09
Critical webs		
t = 0.1	17	+0.67
t = 0.14	18	+0.29
Critical stiffener at BL 28		
WL 150	24	+0.82
WL 140	24	+0.72
WL 130	25	+0.32
	26	+0.33
	26	+0.64
WL 124.7	27	+0.75
		High
Horizontal beam at WL 150		
Upper flange	30	High
Web	30	High
Perimeter beam		
Inboard of BL 13.5	30	+0.09
Outboard of BL 13.5	30	+0.22
Torque box at WL 105		
Tension	35	+0.50
Compression	35	+0.10
Lug backup structure at BL 8.7	36	+0.24

b. Finite Element Analysis of Cast Bulkhead and Transition Structure

Figures 4 through 14 show the details of the finite element model used to determine the internal loads. The model consists of 276 nodes and 895 elements. It represents the structure indicated on figure 3. Figure 4 represents an exploded view of the model, while the detail nodal diagrams are shown on figures 6 through 14.

c. Critical Components Stress Analysis

Figures 15 through 36 contain the strength analysis of the critical components of the bulkhead. The margins of safety are summarized in Section III.1.a.

2. DAMAGE TOLERANCE ANALYSIS

Bulkhead stresses obtained from finite element computer runs were reviewed to determine which points would be considered damage tolerance critical. The details selected for this analysis are:

- o Outer load attachment point A (fig. 37)
- o Shear web located between LBL 28-LBL 32 and WL 124.7-WL 130 (fig. 37)

Damage tolerance analyses were performed on the respective details for the following flaw types:

- o Corner flaw at a clevis hole
- o Surface flaw in a shear web

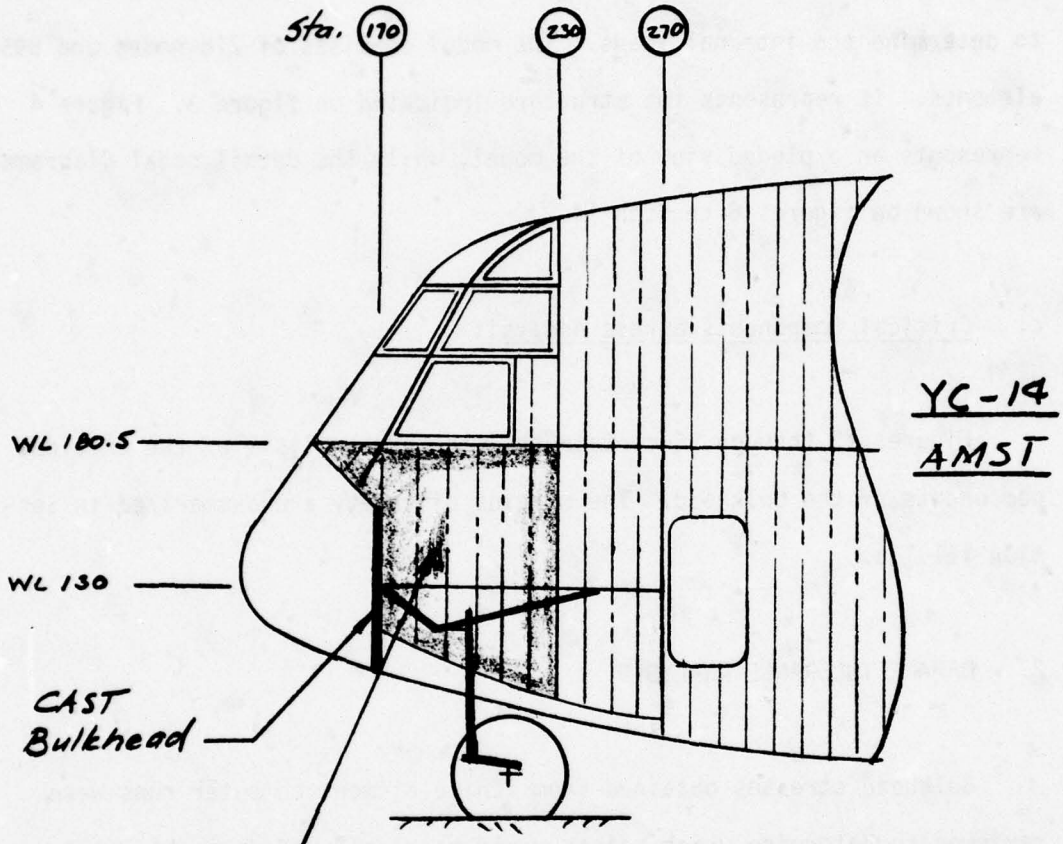

Finite Element Computer Model of CAST Bulkhead and Transition Structure.

ENGR.	C. Ratten	11-28-77	REVISED	DATE	CAST Bulkhead and Transition Structure	CAST
CHECK	BOLLINGER	11-29-77				Fig. 3
APR						
APR					BOEING	24

D1 4100 5320 REV.6/71

J18-047

EXPLODED GEOMETRY

CAST BULKHEAD & TRANSITION STRUCTURE

ENGR.	R. Romero	11-18-77	REVISED	DATE	CAST- FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 4
APR						
APR					BOEING	25

D1 4100 5320 REV.8/71

J18-047

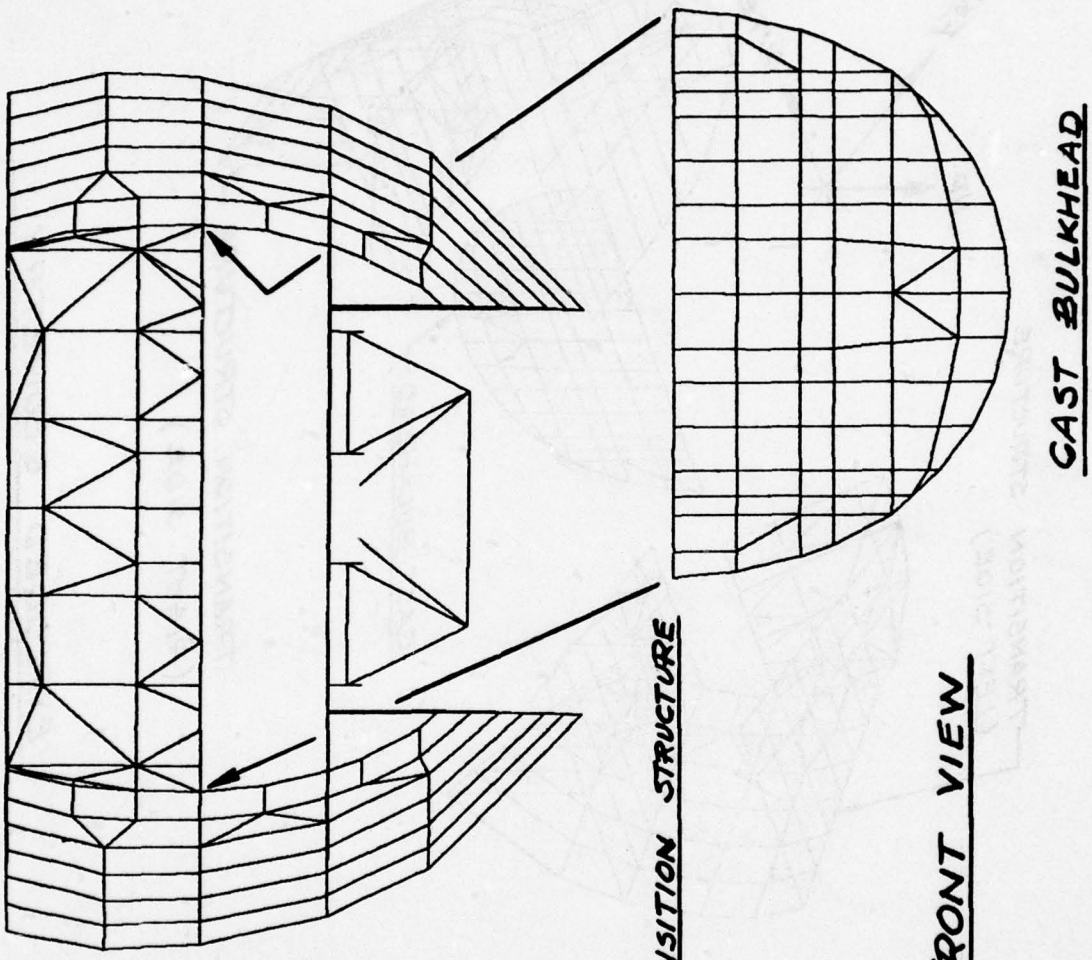

ENGR.	R. Romero	11-18-77	REVISED	DATE	CAST - FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 5
APR						
APR					BOEING	26

D1 4100 5320 REV.6/71

J18-047

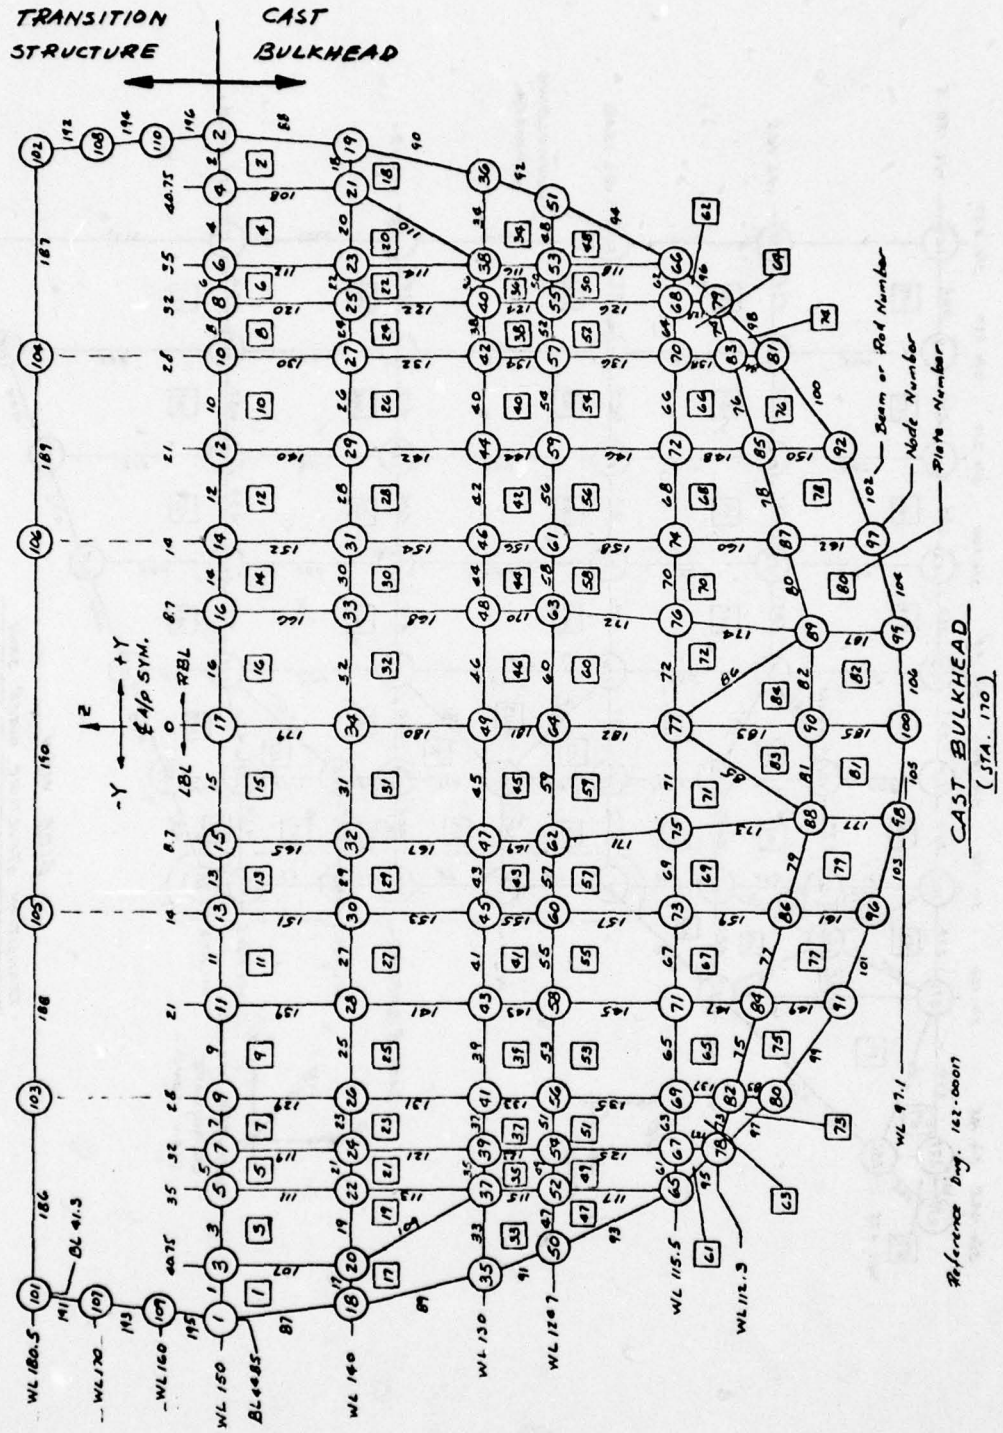

ENGR.	C. Bowers	11-10-77	REVISED	DATE	CAST- FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 6
APR						
APR					BOEING	27

D1 4100 5320 REV. 8/71

J19-047

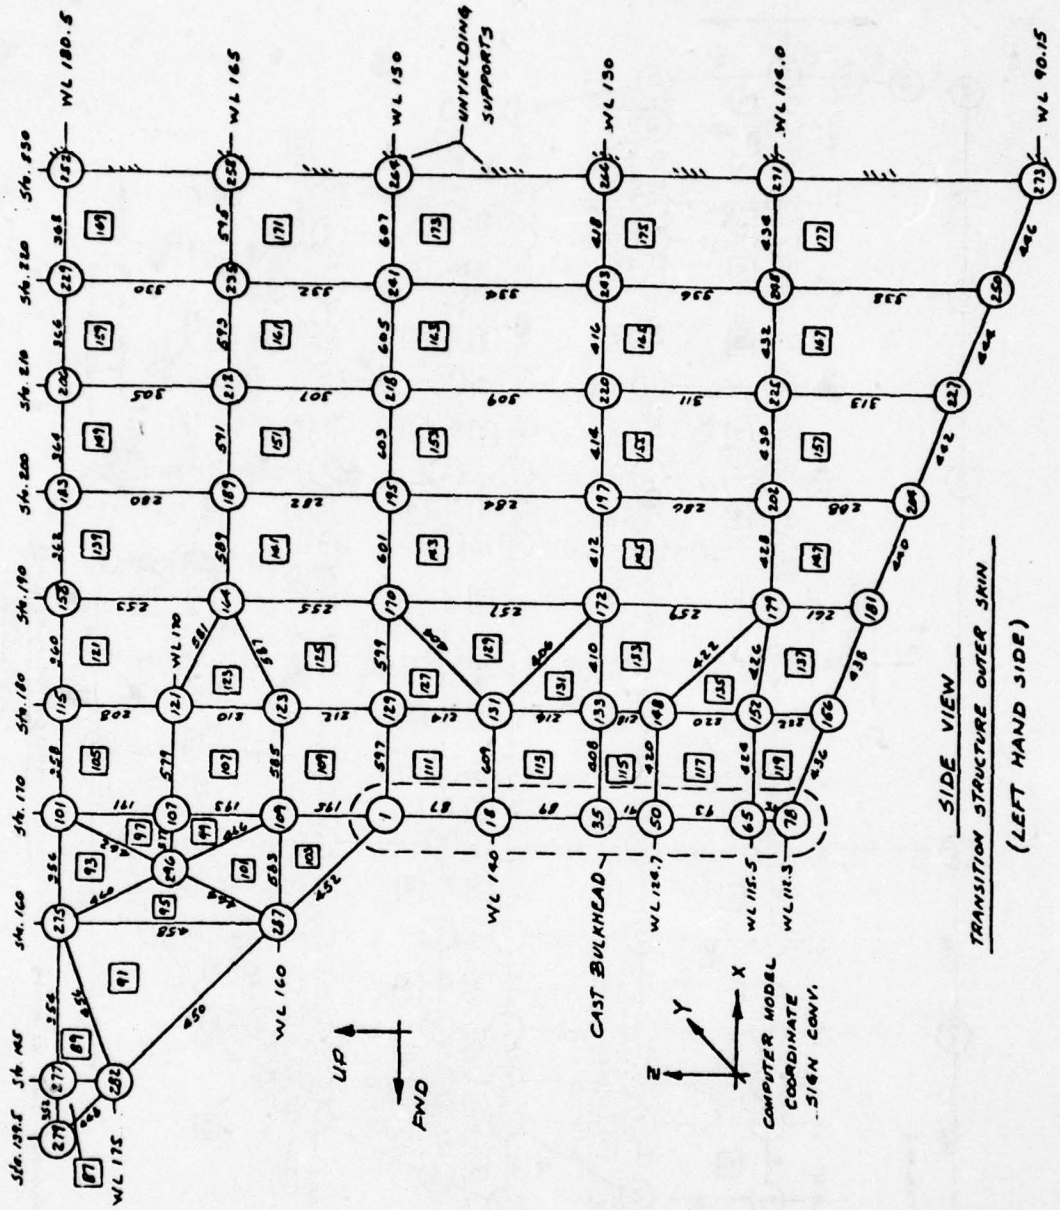

ENGR.	C. Romero	11-10-77	REVISED	DATE	CAST- FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 7
APR						
APR					BOEING	28

D1 4100 9320 REV.8/71

J19-047

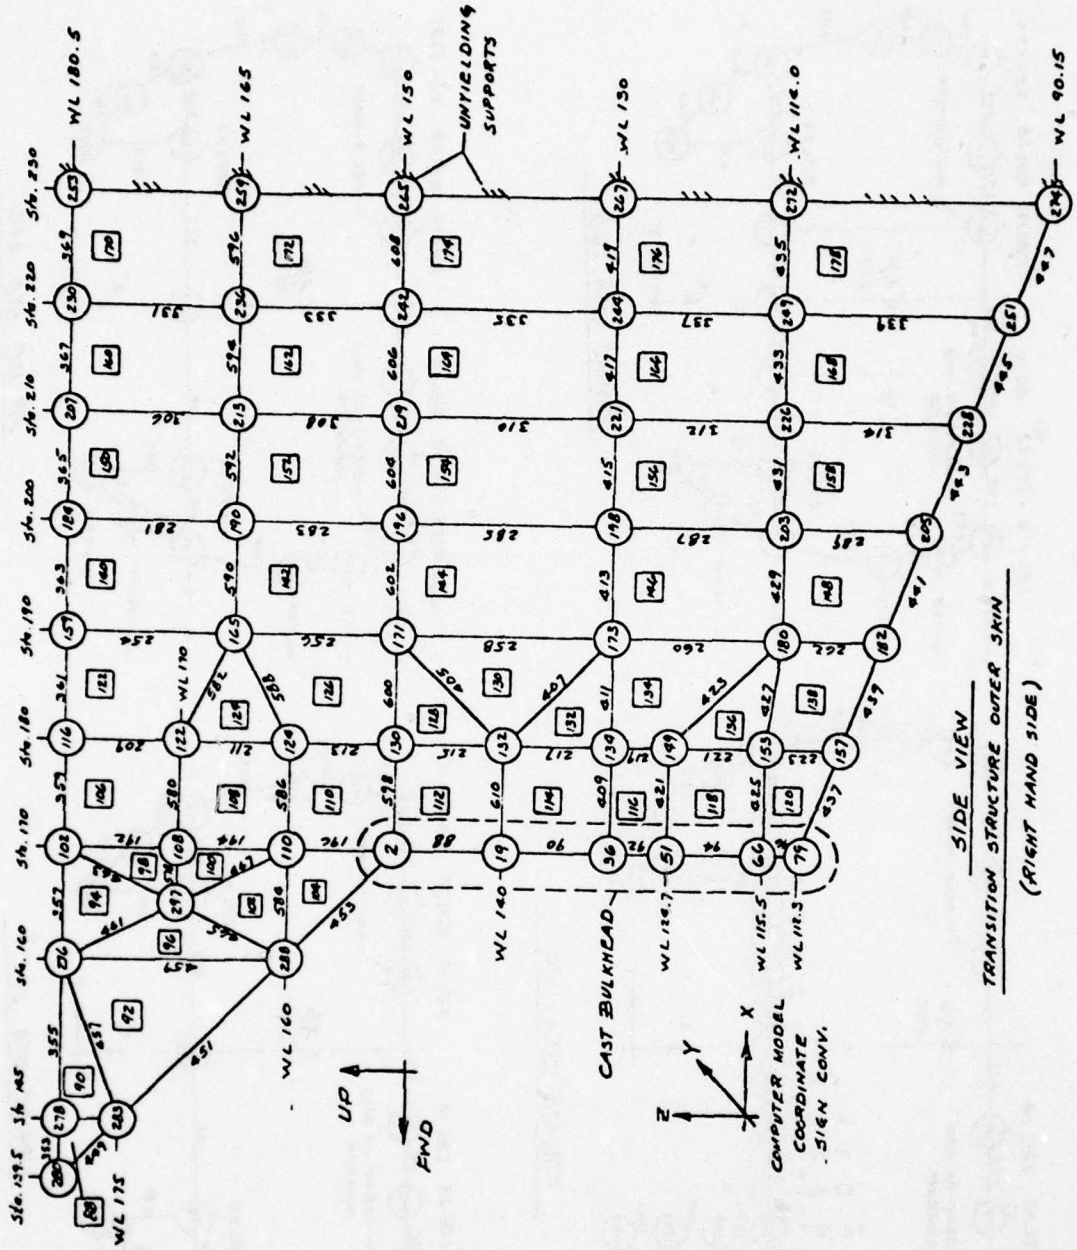

ENGR.	C. Bowers	11-10-77	REVISED	DATE	CAST - FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 8
APR						
APR					BOEING	29

D1 4100 8320 REV. 8/71

J18-047

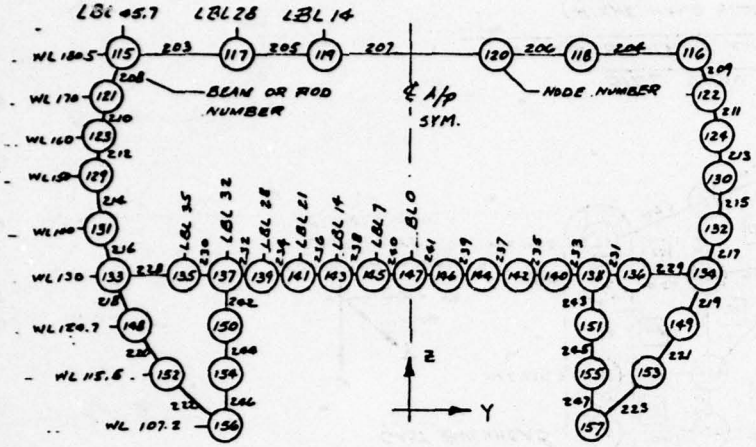

FRAME STA. 180

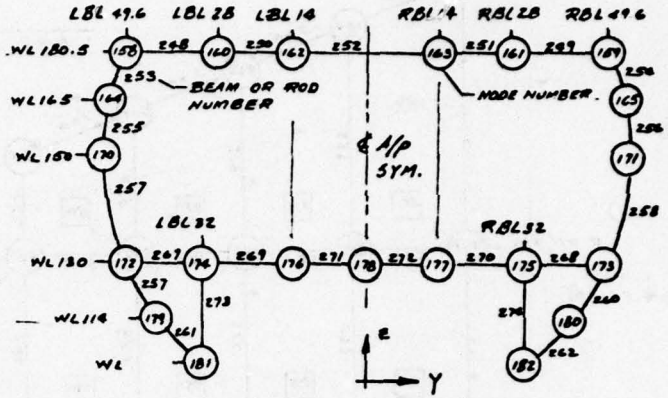

FRAME STA. 190

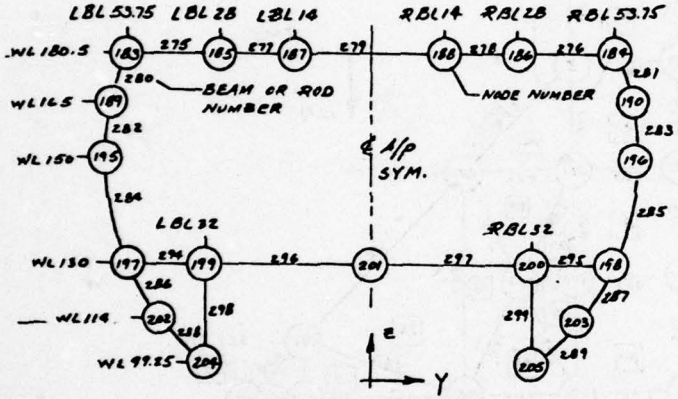

FRAME STA. 200

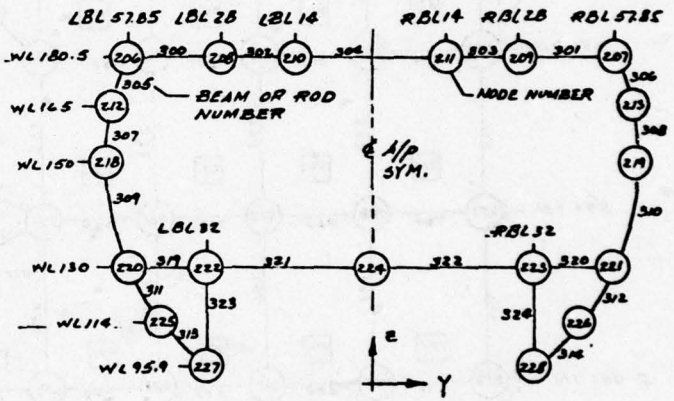

FRAME STA. 210

					ENGR.	
					CHECK	BOLLINGER 11-29-71
					APR	11-30-72
					APR	
				REVISED		
				DATE		

BOEING

CAST - FINITE ELEMENT COMPUTER MODEL

CAST Fig. 9

30

D1 4100 5320 REV. 8/71

J18-042

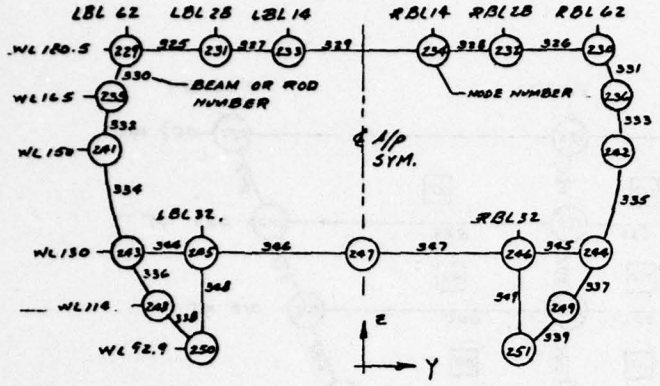

— FRAME STA. 220

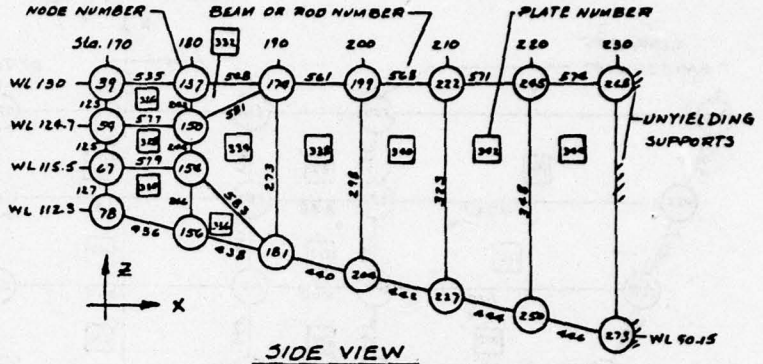

SIDE VIEW
BEAM AT BL 32 (LEFT SIDE)

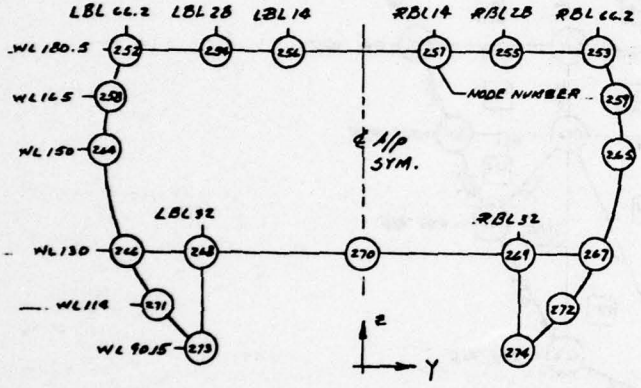

— FRAME STA. 230

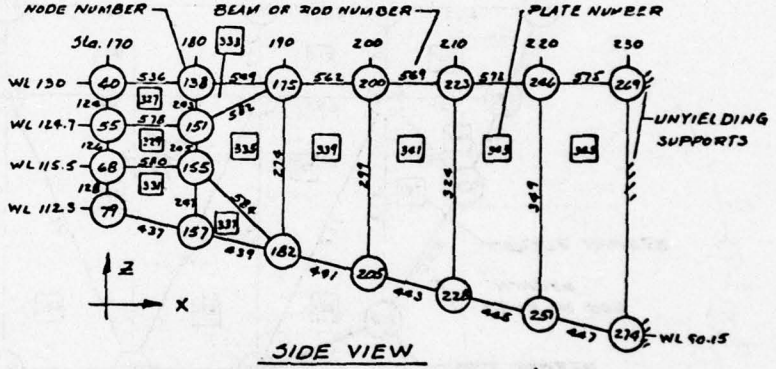

SIDE VIEW
BEAM AT BL 32 (RIGHT SIDE)

						ENGR.	E. Hooton
						CHECK	BOLLINGER 11-29-71
						APR	
						APR	
					REVISED	DATE	
CAST - FINITE ELEMENT COMPUTER MODEL							CAST
BOEING							Fig. 10
							31

D1 4100 5320 REV. 8/71

J10-047

PLAN VIEW
(WL 180.5)

ENGR.	C. Romero	11-10-77	REVISED	DATE	CAST - FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 11
APR						
APR					BOEING	32

D1 4100 8320 REV. 8/71

J15-047

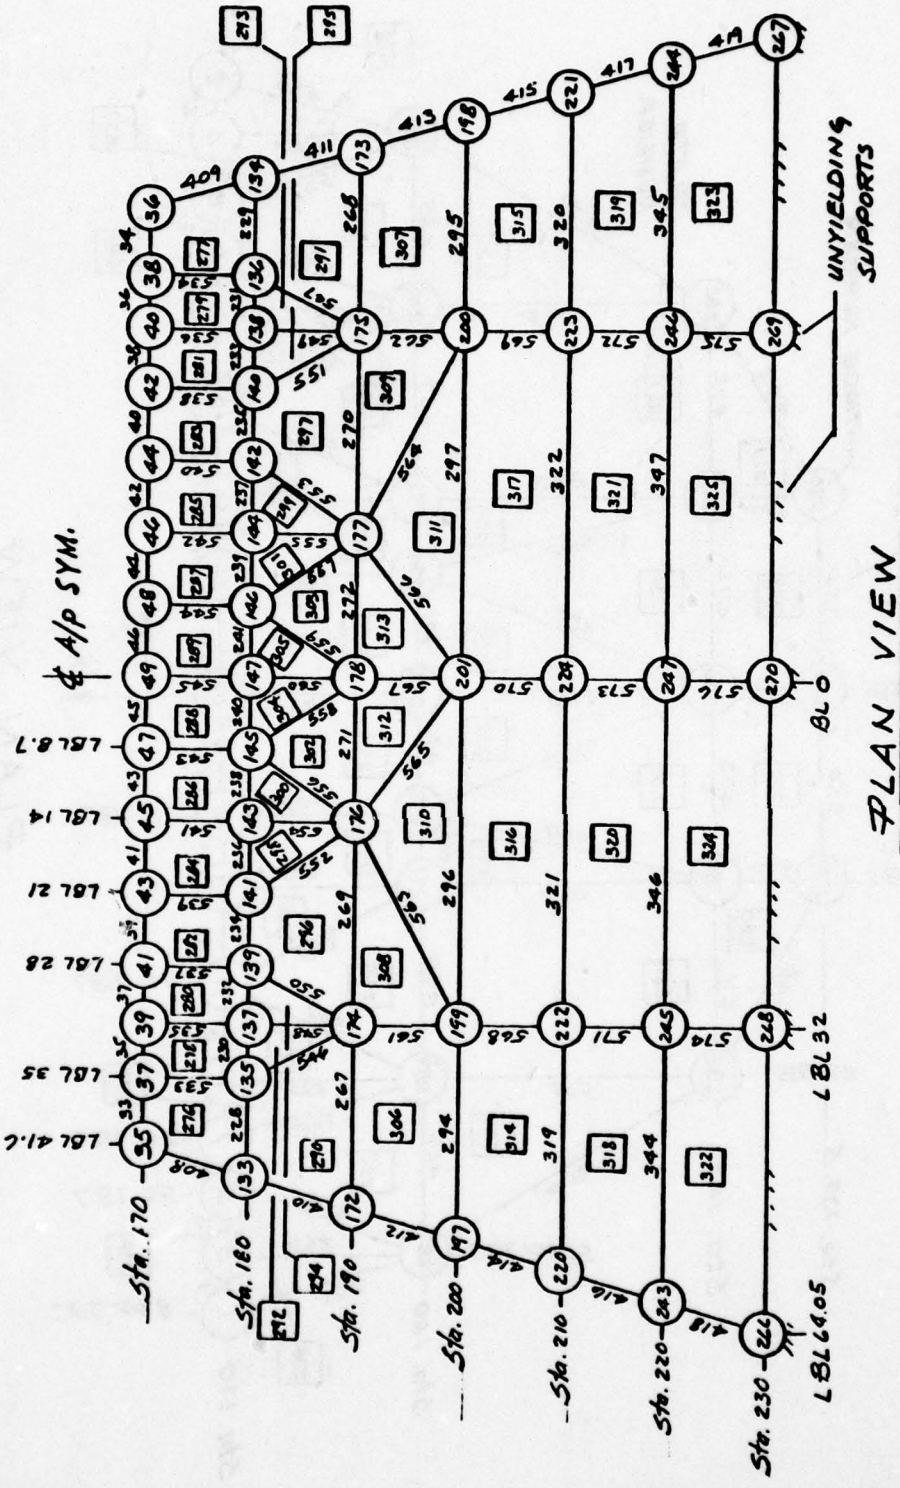

PLAN VIEW
(WL 130)

ENGR.	T. Romero	11-11-71	REVISED	DATE	CAST- FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-71				Fig. 12
APR						
APR					BOEING	33

D1 4100 5320 REV. 8/71

J15-047

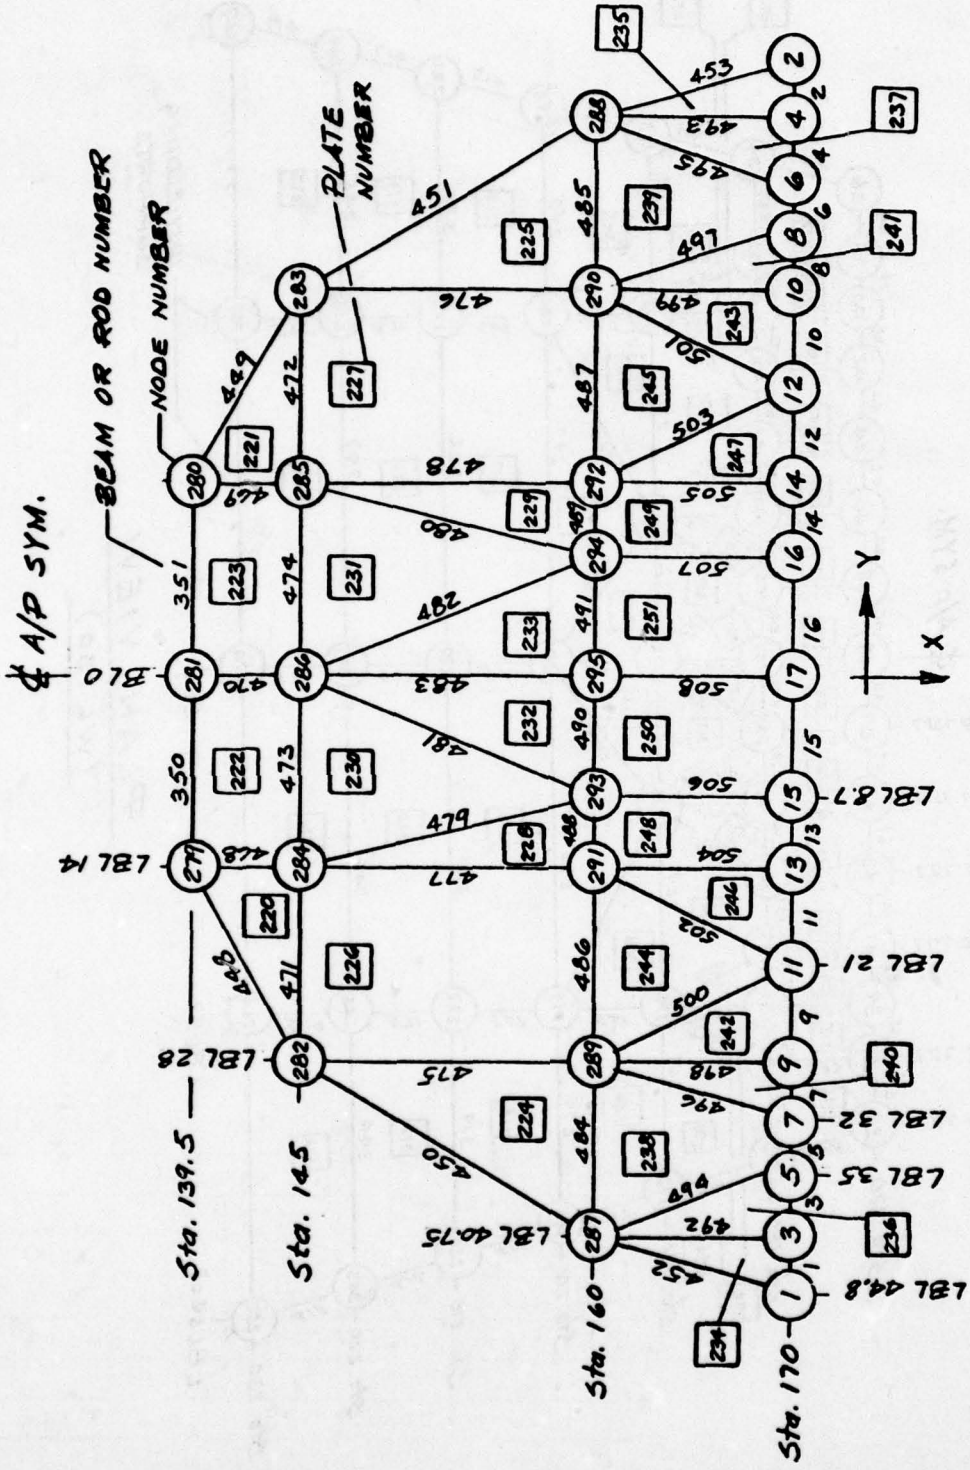

PLAN VIEW
(CANTED BULKHEAD)

ENGR	A Romeo	11-1-77	REVISED	DATE	CAST- FINITE ELEMENT COMPUTER MODEL	CAST
CHECK	BOLLINGER	11-29-77				Fig. 13
APR						34
APR					BOEING	

D1 4100 3320 REV. 8/71

J18-047

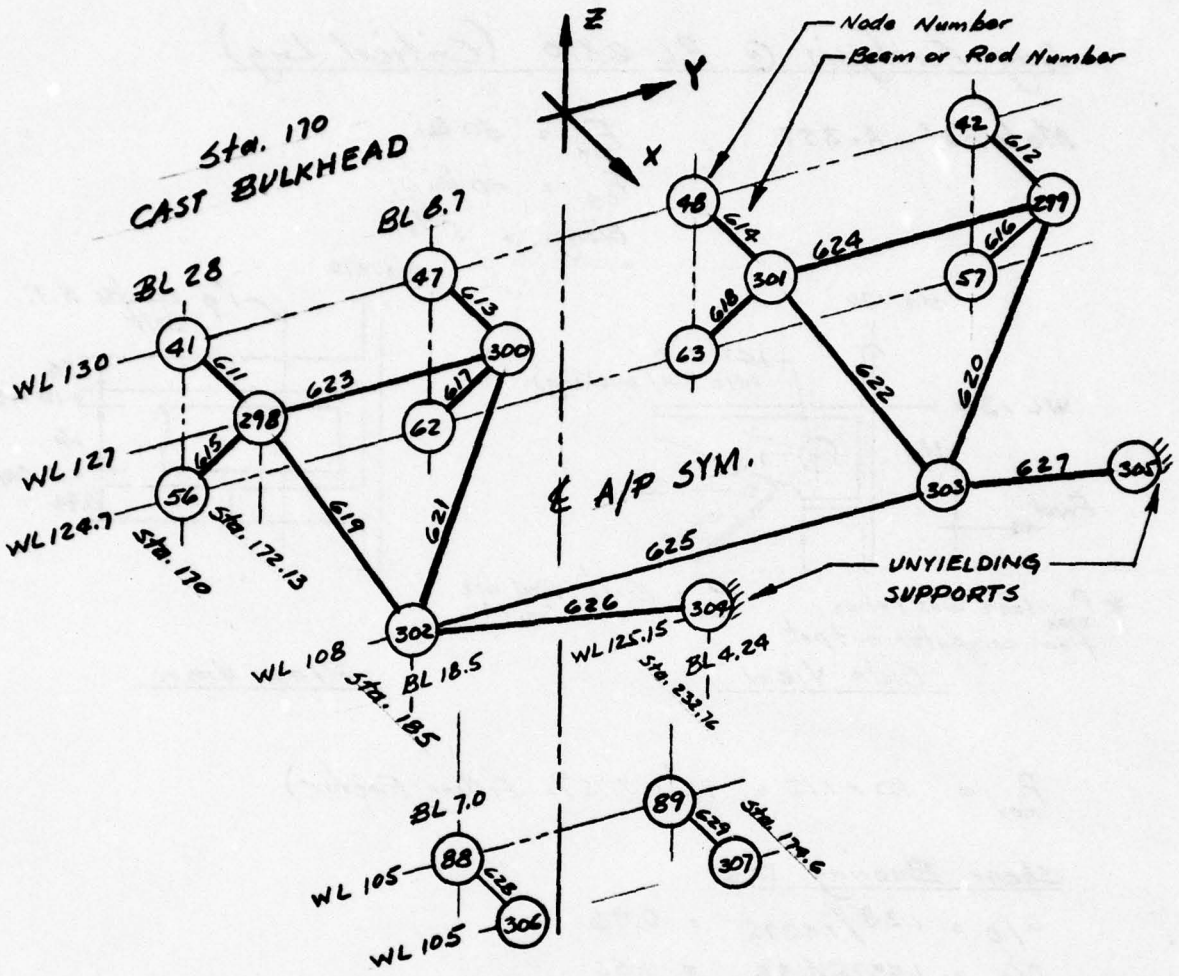

LANDING GEAR BACK-UP STRUCTURE & LANDING GEAR DOOR ACTUATOR SUPPORT

LOAD CONDITION	LOCATION & LOAD* APPLIED ON STRUCTURE					
	NODE 302			NODE 303		
	F_x	F_y	F_z	F_x	F_y	F_z
Landing - Spring Back	-31.84	0	79.5	-22.56	0	56.91
Boeing Side Load	-1.44	-22.5	98.89	-56.16	-22.5	-78.4
3 Point Braked Roll	-102.6	0	-3.8	-109.4	0	-37.7
Landing Gear Door Actuator Jammed Load	NODE 306			NODE 307		
	0	-27.0	-21.2	0	-11.5	36.0

* All loads are in kips & ultimate.

ENGR.	A. Ramero	11-14-77	REVISED	DATE	CAST - FINITE ELEMENT COMPUTER MODEL APPLIED LOADS	CAST Fig. 14
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	35

D1 4100 8320 REV. 8/71

J18-047

Lug Analysis @ BL 28.0 (Critical Lug)

Material - A-357

F_{tu} = 50 ksi

F_{ty} = 40 ksi

Elong. = 5%

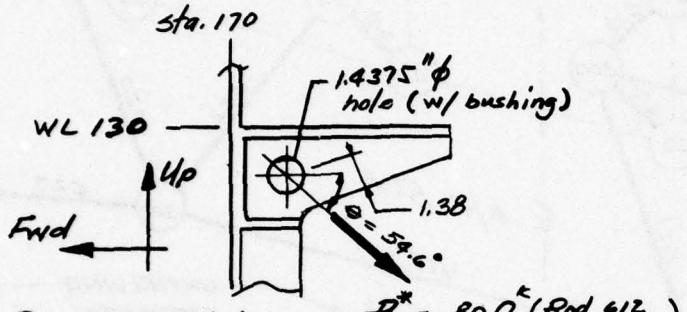

* P_{max} load was taken from computer output

Side View

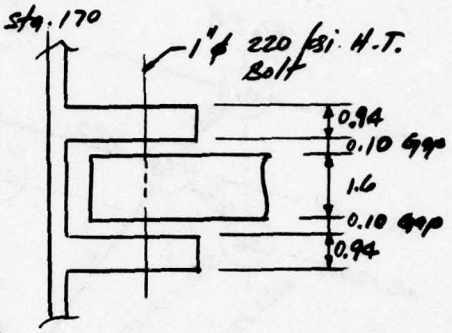

Plan View

P_{max} = 80 x 1.15 = 92k (15% Fitting Factor)

Shear Bearing [1]

a/D = 1.38/1.4375 = 0.96

D/t = 1.4375/0.94 = 1.53

k_{br} = 0.77 (Fig. 13 pg. 167)

$P_{brg} = k_{br} F_{tu} D t$ = 0.77 x 50 x 1.4375 x 1.88 = 104.0k

M.S. = 104/92 - 1 = +0.13

Tension [1] (Assume W = 3.0)

W/D = 3.0/1.4375 = 2.09

k_t = 0.682 (Fig. 12 pg. 166)

$P_t = k_t (W-D) F_{tu} t$ = 0.682 (3-1.4375) 50 x 1.88 = 100.2k

M.S. = 100.2/92 - 1 = +0.09

[1] Lug Analysis Structural Bulletin 1.712 Product Eng. June 1953

ENGR.	C Romero	11-15-77	REVISED	DATE	CAST Bulkhead Critical Lug @ BL 28	CAST Fig. 15
CHECK	BOLLINGER	11-29-77				
APR					BOEING	36
APR						

D1 8007 2070 ORIG. 6/73

J18-047

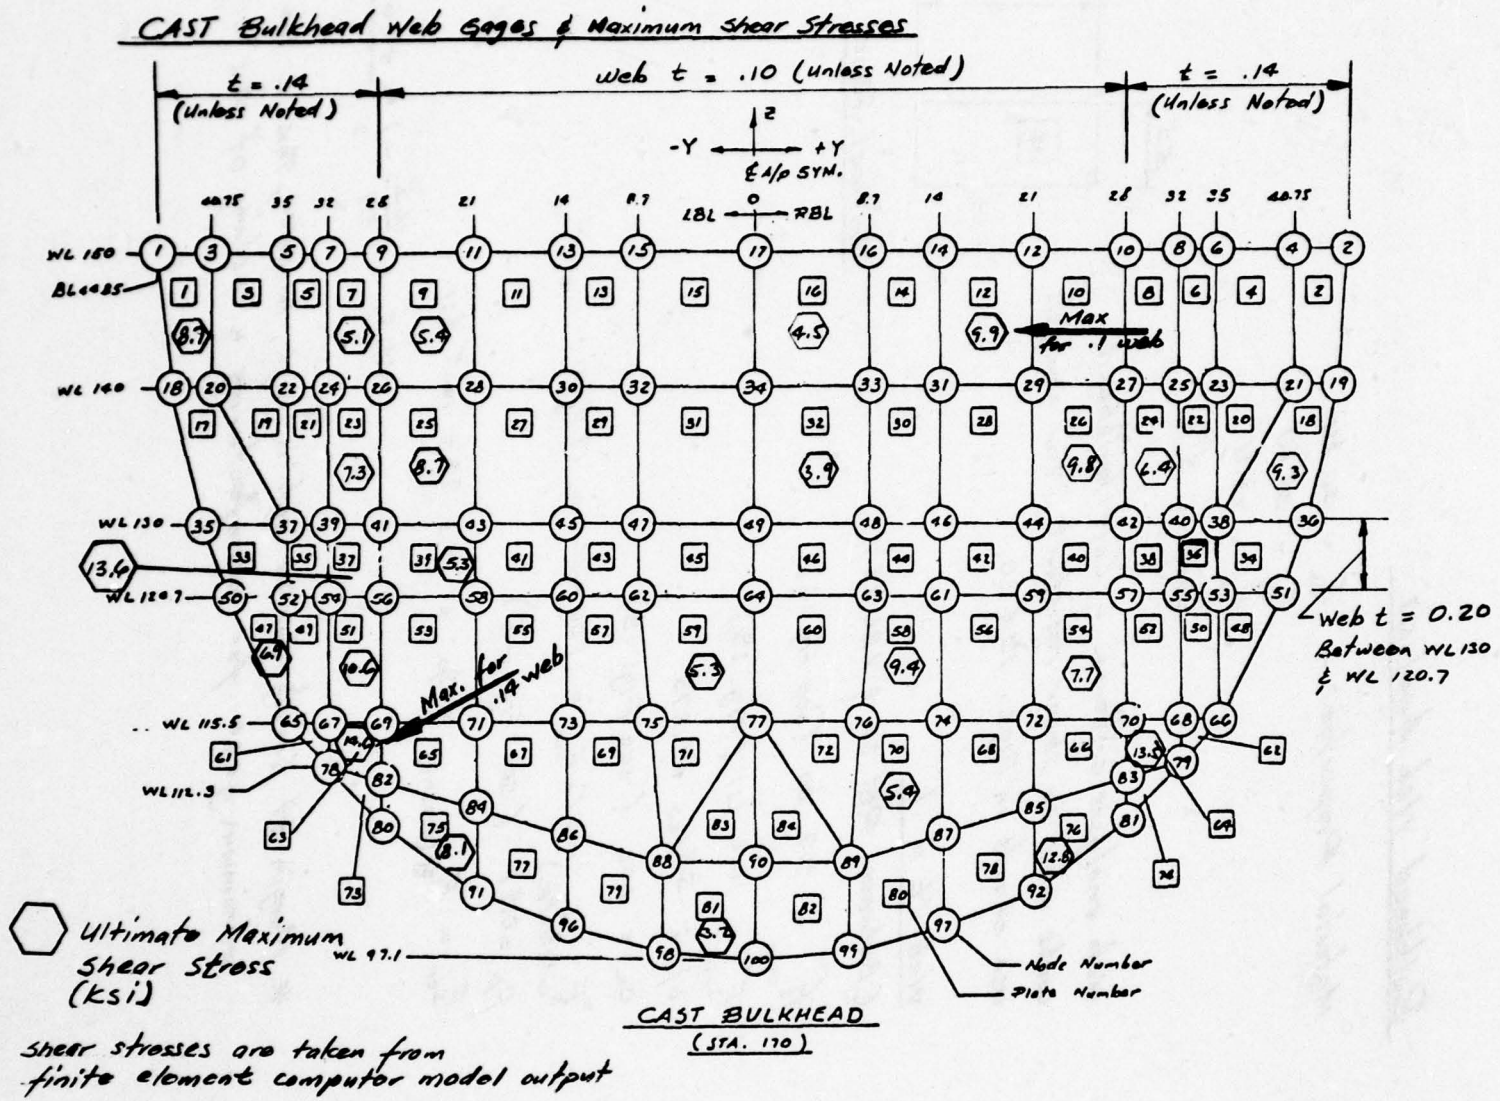

ENGR.				
CHECK	BOLLINGER	11-29-77		
APP				
APP				

CAST BULKHEAD
Web GAGES & STRESSES
BOEING

CAST
Fig. 16
37

D1 4100 8220 REV. 8/71

J19-047

Bulkhead Web Analysis

Material Properties – F_{tu} = 40 ksi
F_{ty} = 30 ksi
F_{su} = 28 ksi
Elong. = 3%

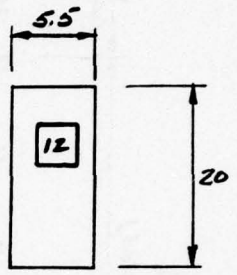

Critical Panel

Web analysis criteria – Cast bulkhead webs must be shear resistant. For analysis use charts in Figs. 19 & 20.

Web t = .1
(Between RBL 28 & LBL 28)

$f_{s_{max}}$ = 9.9 ksi (see Fig. 16)
$F'_{s_{cr}}$ = 16.0 ksi (Fig. 19)
b/a = 5.5/20 = 0.275
C_a = 1.06 (see Fig. 19)
$F_{s_{cr(elastic)}} = C_a F'_{s_{cr}}$ = 1.06 × 16 = 17.0 ksi.
C_p = 0.97 (see Fig. 20)
$F_{s_{cr}} = F_{s_{cr(elastic)}} \times C_p$ = 17 × .97 = 16.5 ksi.

$$M.S. = \frac{16.5}{9.9} - 1 = +0.67^{*}$$

* Margin of Safety for 0.1 web is high, however, this is the minimum gage for manufacturing a casting of this size.

ENGR.	A. Romero	11-14-77	REVISED	DATE	CAST Bulkhead Web (t = 0.1)	CAST
CHECK	BOLLINGER	11-29-77				Fig. 17
APR						
APR					BOEING	38

Bulkhead Web Analysis (Cont'd.)

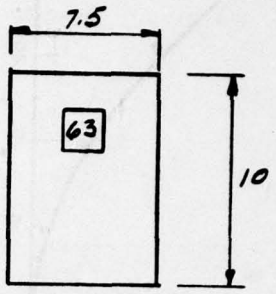

Critical Panel

Web t = 0.14

(Between BL 45 & BL 28)

For analysis use charts in Figs. 19 & 20

f_s = 14.6 ksi (Fig. 16)

$F'_{s_{cr}}$ = 18.0 ksi (see Fig. 19)

b/a = 7.5/10 = 0.75

Ca = 1.42 (Fig. 19)

$F_{s_{cr}(elastic)} = Ca \times F_{s_{cr}} = 1.42 \times 18 = 25.6$ ksi

C_p = 0.77 (Fig. 20)

$F_{s_{cr}} = C_p \times F_{s_{cr}(elastic)} = 0.77 \times 25.6 = 19.7$ ksi.

Combine shear w/ Tension -

P = 8.9^k (Bm 137 axial load Fig. 21)

A = 0.96 in^2

P/A = 8.9/0.96 = 9.3 ksi < 40 ksi (F_{tu})

R_s = 14.6/19.7 = 0.74

R_t = 9.3/40 = 0.23

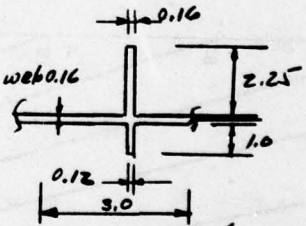

Cross-section (Bm 137)

$$M.S._{(shear + ten.)} = \frac{1}{\sqrt{R_s^2 + R_t^2}} - 1 = +0.29$$

ENGR.	A. Romero	11-14-77	REVISED	DATE	CAST Bulkhead Web (t = 0.14)	CAST Fig. 18
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	39

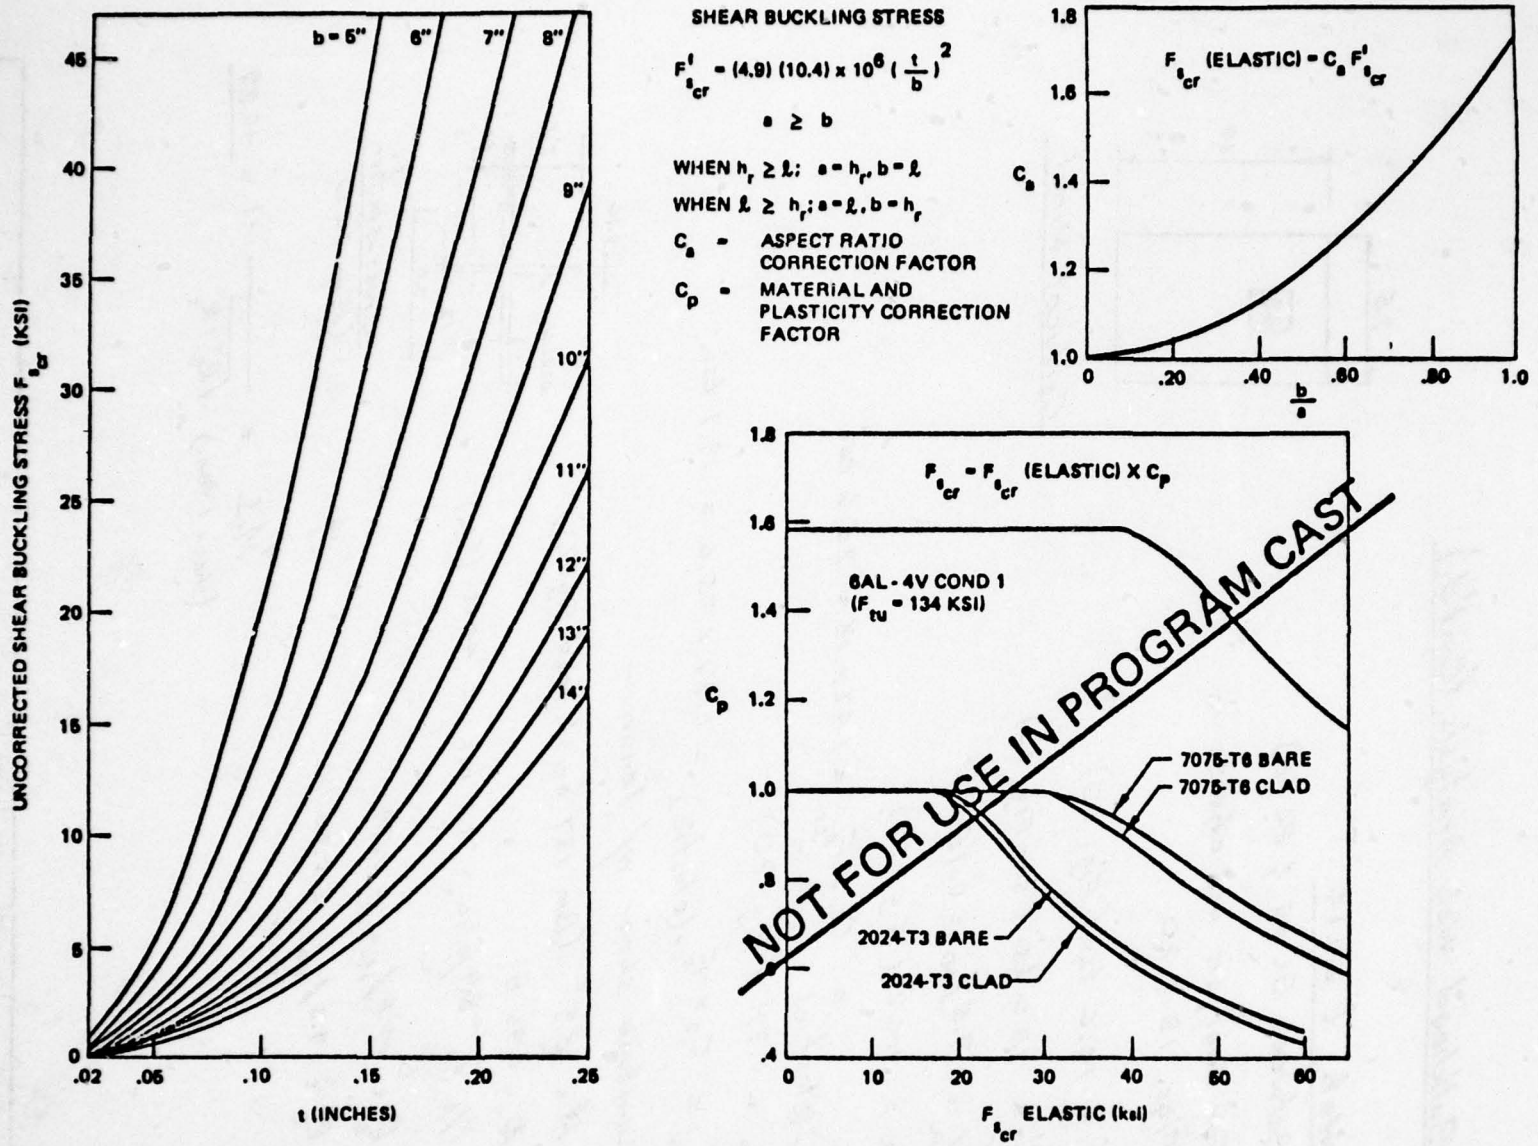

(Boeing Design Manual) Figure 19. Web Ultimate Shear Stress (Shear Resistant Web Design)

WEB BUCKLING (SHEAR)

PROGRAM CAST

A357-T6 CASTINGS		70°F
CL I	50/40/5	
CL II	45/35/3	
CL III	40/30/3	
CL IV	35/30/5	

PRELIMINARY DESIGN ALLOWABLES

S-BASIS

FOR USE WITH FIGURE 8.2.1.1-1 OF DM86B1

$F_{SCR} = F_{SCR\ (ELASTIC)} \cdot C_P$

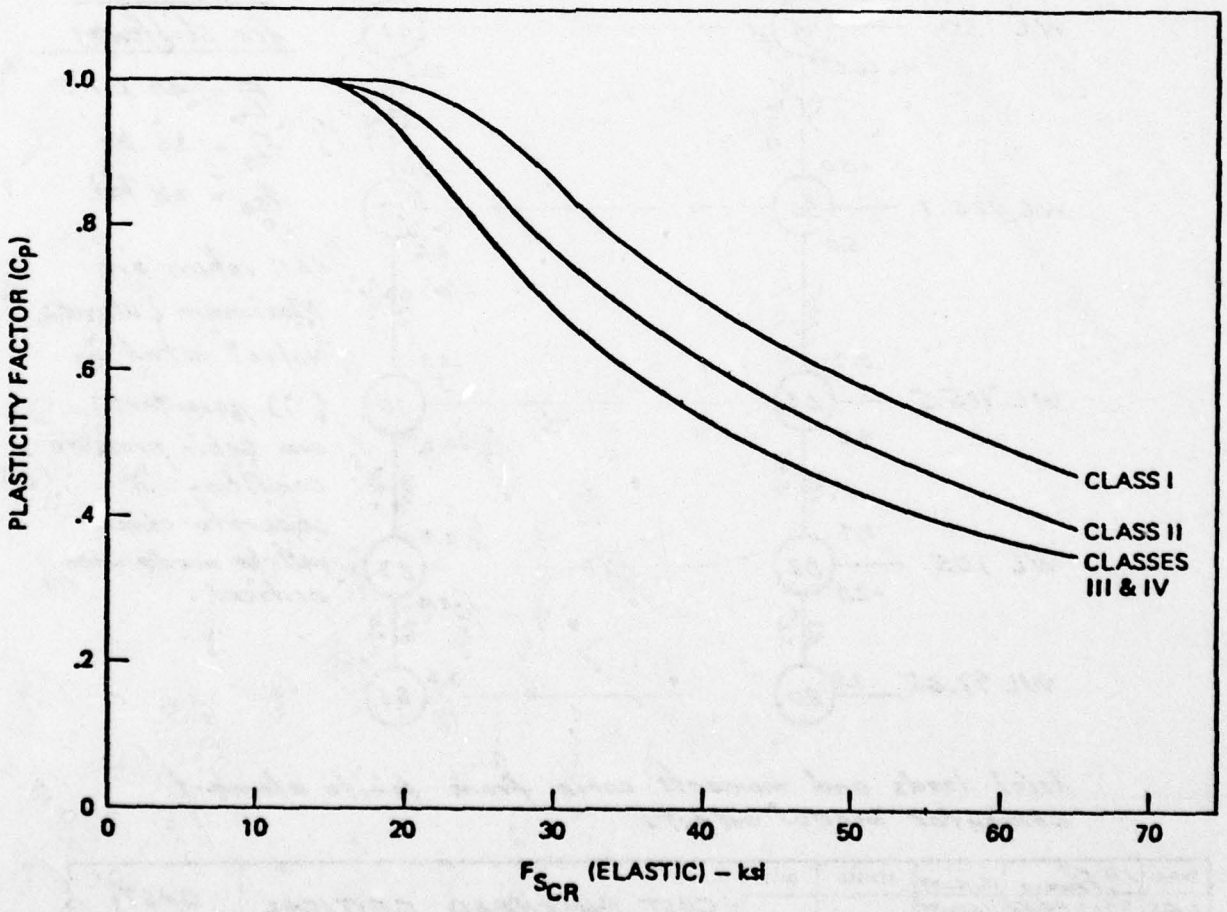

(Boeing Design Manual) Figure 20. Shear Resistant Web Design

Stiffeners @ LBL 28 & RBL 28 Axial Loads & Moments

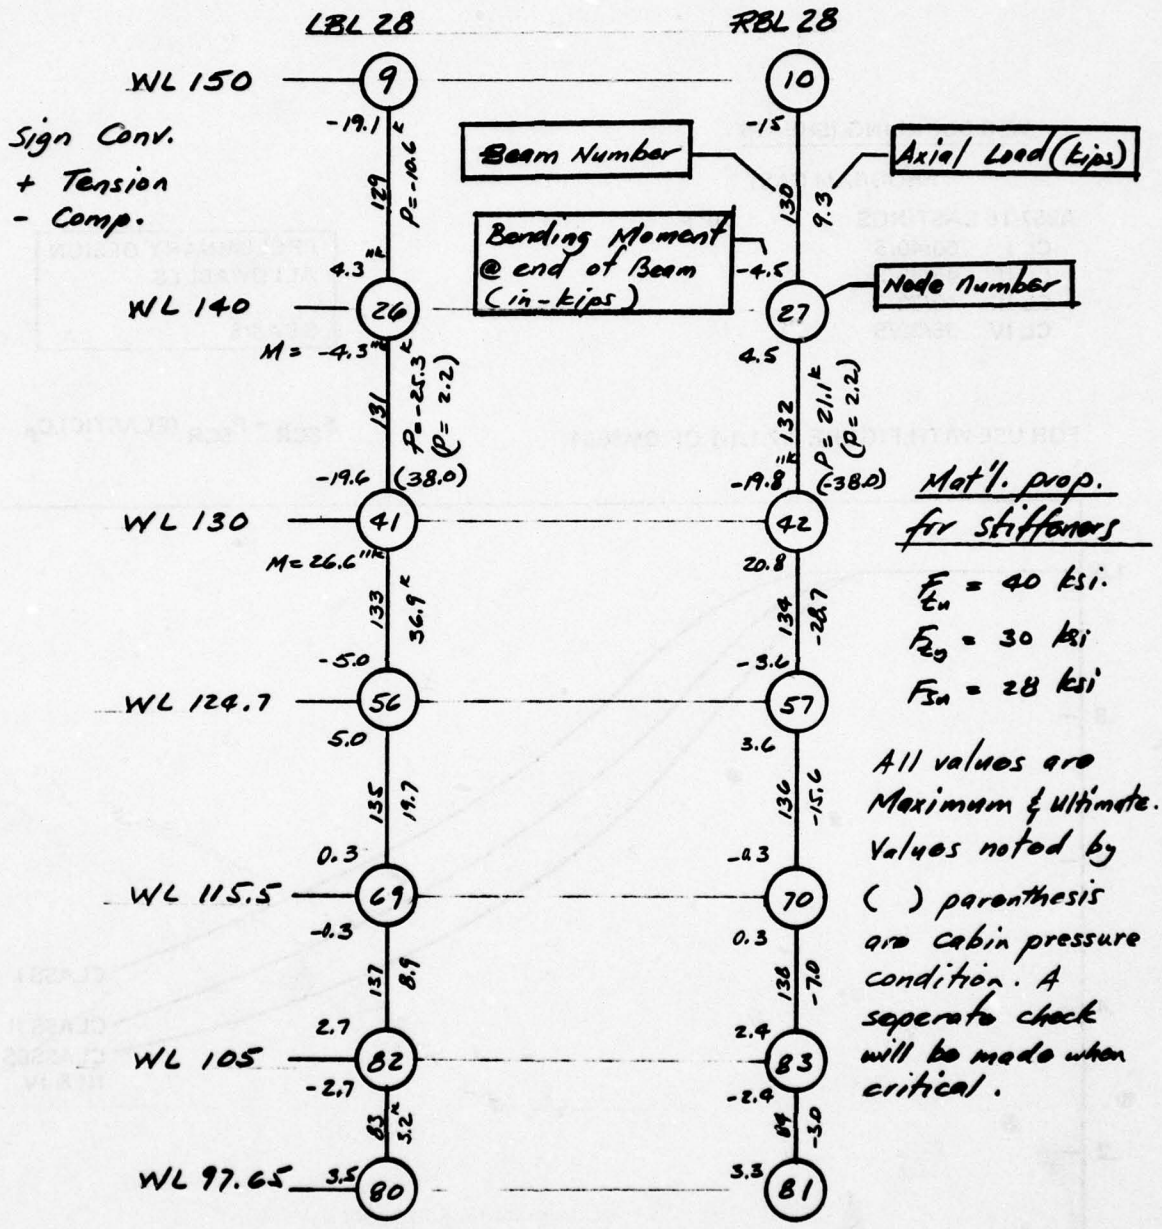

Mat'l. prop. for stiffeners

F_{tu} = 40 ksi.

F_{cy} = 30 ksi

F_{su} = 28 ksi

All values are Maximum & Ultimate. Values noted by ( ) parenthesis are cabin pressure condition. A seperate check will be made when critical.

Axial loads and moments come from finite element computer model output.

ENGR.	C. Romero	11-16-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST
CHECK	BOLLINGER	11-29-77				Fig. 21
APR						
APR					BOEING	42

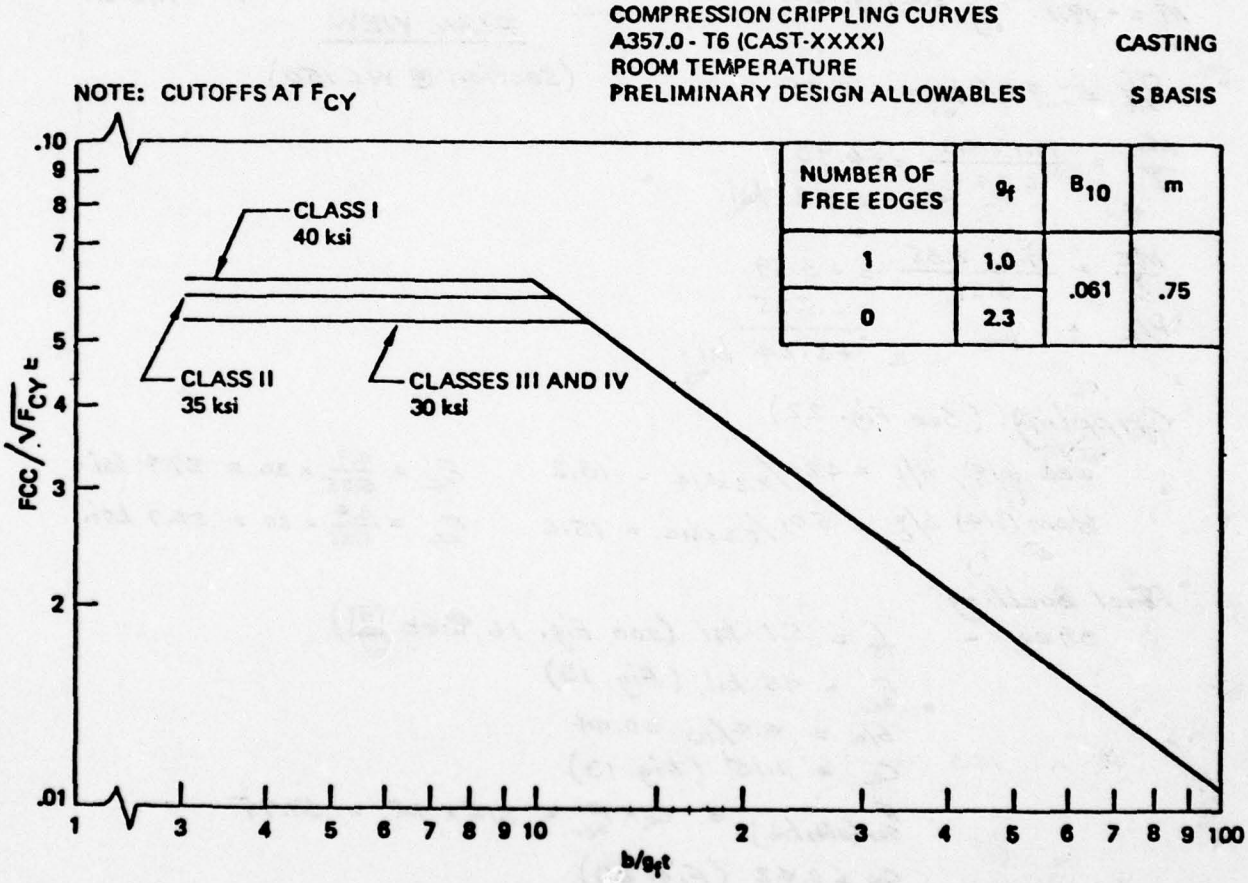

Figure 22. Compression Crippling Curves

Section @ WL 150

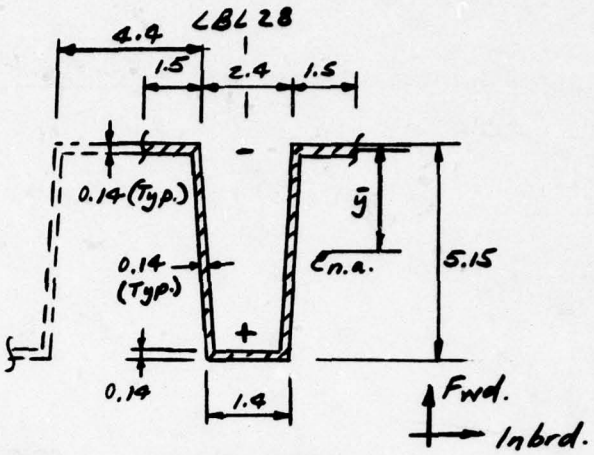

PLAN VIEW
(section @ WL 150)

Section Properties -

$A = 1.98\ in^2$

$\bar{y} = 2.3$

$I = 6.34\ in^4$

$P = -10.6^{k}$ } Bm 129
$M = 19.1^{in^k}$ } see Fig. 21.

$P/A = -10.6/1.98 = -5.35$

$\frac{Mc}{I} = \frac{19.1 \times 2.3}{6.34} = -6.93$

-12.28 ksi.

$\frac{Mc}{I} = \frac{19.1 \times 2.85}{6.34} = +8.59$

$P/A = -5.35$

$+3.24$ ksi.

Crippling (See Fig. 22)

web (0.14) $b/t = 4.26/2.3 \times 0.14 = 13.2$ $\quad F_{cc} = \frac{9.9}{5.35} \times 30 = 27.4$ ksi.

stem (0.14) $b/t = 5.01/2.3 \times 0.14 = 15.6$ $\quad F_{cc} = \frac{9.9}{6.35} \times 30 = 24.7$ ksi.

Panel Buckling -

shear - $f_s = 5.1$ ksi (see Fig. 16, web [7])

$F'_{scr} = 45$ ksi (Fig. 19)

$b/a = 4.4/10 = 0.44$

$C_a = 1.15$ (Fig. 19)

$F_{scr(elastic)} = C_a \times F'_{scr} = 1.15 \times 45 = 51.75$

$C_p = 0.42$ (Fig. 20)

$F_{scr} = C_p \times F_{scr(elastic)} = 0.42 \times 51.75 = 21.7$ ksi.

ENGR.	C. Romero	11-16-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST
CHECK	BOLLINGER	11-29-77				Fig. 23
APR					BOEING	44
APR						

Section @ WL 150 (Cont'd.)

Panel Buckling -

Compression - Aircraft Structures by Perry pg. 372 Fig. 14.25

$a/b = 10/4.4 = 2.27$

$k = 3.6$ (4 sides simply supported)

$F_{c_{cr}} = kE(t/b)^2$

$F_{c_{cr}} = 3.6 \times 10.4 \times 10^3 (.14/4.4)^2 = 37.9$ ksi > 30 ksi (F_{cy})
buckling is not critical

Combined Compression & Shear -

$R_c = f_c/F_{cc} = 12.28/24.7 = 0.497$

$R_s = f_s/F_{s_{cr}} = 5.1/21.7 = 0.235$

$$M.S. \text{ (Comp. + shear)} = \frac{1}{\sqrt{R_c^2 + R_s^2}} - 1 = \underline{+0.82}$$

Section @ WL 140

Section Properties -

$A = 1.66$ a"

$\bar{y} = 1.74$

$I = 3.38$ in^4

$P = \frac{10.6 + 25.3}{2} = 17.95^k$ } Bms 129 & 131 see Fig. 21.

$M = 4.3^{11K}$

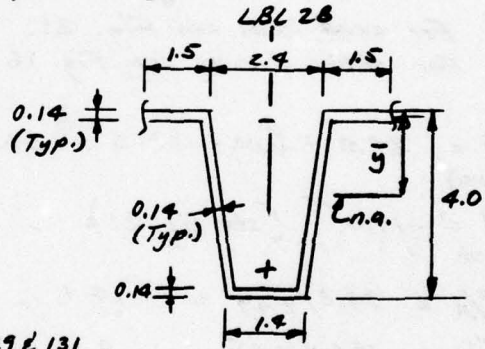

PLAN VIEW
(Section @ WL 140)

$P/A = 17.95/1.66 = -10.8$

$\frac{Mc}{I} = \frac{4.3 \times 1.74}{3.38} = -\frac{2.2}{13.0}$ ksi. $<$ 27.4 ksi. (F_{cc} prev. pg.)

$f_s = 7.3$ ksi (Fig. 16, web [23]) $<$ 21.7 ksi ($F_{s_{cr}}$ prev. pg.)

$R_s = f_s/F_{s_{cr}} = 7.3/21.7 = 0.336$

$R_c = f_c/F_{cc} = 13/27.4 = 0.474$

$$M.S. \text{ (comp + shear)} = \frac{1}{\sqrt{R_s^2 + R_c^2}} - 1 = \underline{+0.72}$$

ENGR.	O. Romero	11-K-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST Fig. 24
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	45

Section @ WL 130

$A = 2.47\ \square''$

$\bar{y} = 0.95$

$I = 4.88\ in^4$

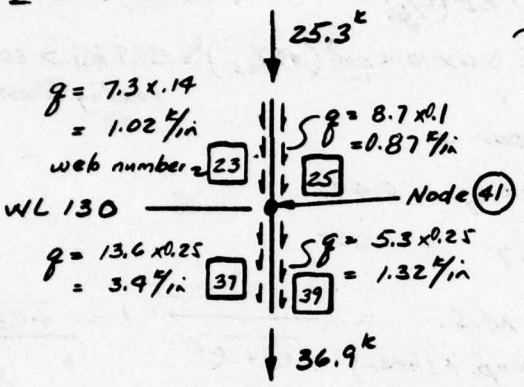

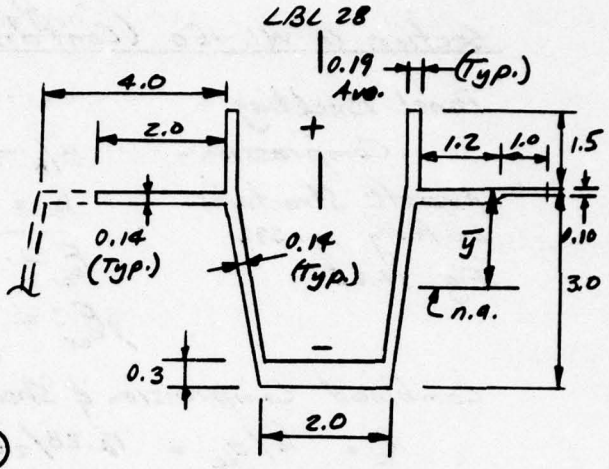

PLAN VIEW
(Section @ WL 130)

For axial loads see Fig. 21.
For shear stresses see Fig. 16.

$P = 25.3 + (1.02 + .87)\,5 = 34.8^k$ (@ WL 130)

$M = -19.6^{11k}$ (see Fig. 21) (@ WL 130)

$P/A = 34.8/2.47 = -14.1$

$\frac{Mc}{I} = \frac{19.6 \times 2.05}{4.88} = -8.2$ $\qquad$ $\frac{Mc}{I} = \frac{19.6 \times 2.45}{4.88} = +9.8$

$f = -22.3$ ksi. $\qquad$ -14.1 / -4.3 ksi

$f_s = 1.02/0.3 = 3.4$ ksi. $< F_{su} = 28$ ksi

Combined compression & shear -

$R_c = f_c/F_{cy} = 22.3/30 = 0.743$

$R_s = f_s/F_{su} = 3.4/28 = 0.121$

$M.S. = \frac{1}{\sqrt{R_c^2 + R_s^2}} - 1 = +0.32$ (Extreme fiber)

ENGR.	A. Romero	11-16-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST Fig. 25
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	46

Section @ WL 130 (Cont'd.)

Check location 0.3 from extreme fiber (see sketch prev. pg.) -

$$\frac{Mc}{I} = \frac{19.6 \times 1.75}{4.88} = -7.0$$

$$P/A = \text{prev. pg.} = \frac{-14.1}{-21.1 \text{ ksi.}} < 30 \text{ ksi.} (F_{cy})$$

$$f_s = 1.02/0.14 = 7.3 \text{ ksi.} (\text{prev. pg.}) < 28 \text{ ksi.} (F_{su})$$

Combined comp. & shear -

$$R_c = 21.1/30 = 0.703$$

$$R_s = 7.3/28 = 0.261$$

$$M.S. \underset{(\text{.3 from extreme fiber})}{=} \frac{1}{\sqrt{R_c^2 + R_s^2}} - 1 = \underline{+.33}$$

Check Pressure Case -

$P = 2.2^{\text{C}}$
$M = 38.0^{\text{in-k}}$
} Bm 132 See Fig. 21. Note: moment is reversed from previous critical condition. Shear is small, neglect.

$$P/A = 2.2/2.47 = 0.9$$

$$\frac{Mc}{I} = \frac{38 \times 2.05}{4.88} = \frac{16.0}{16.9 \text{ ksi.} < 40 \text{ ksi.} (F_{tu})}$$

$$P/A = 2.2/2.47 = +0.9$$

$$\frac{Mc}{I} = \frac{38 \times 2.95}{4.88} = \frac{-19.1}{-18.2 \text{ ksi} < 30 \text{ ksi} (F_{cy})}$$

$$M.S. \underset{(\text{pressure case})}{=} \frac{30}{18.2} - 1 = \underline{+0.64}$$

ENGR.	C. Rowe	11-17-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST Fig. 26
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	47

Section @ WL 124.7

$A = 1.97$ □"

$\bar{y} = 2.39$

$I = 1.28$ in^4

$P = -15.6^k$ } Bm 136
$M = 3.6^{in-k}$ } see Fig. 21.

$P/A = 15.6/1.97 = -7.9$

$\frac{Mc}{I} = \frac{3.6 \times 2.39}{1.28} = \frac{-6.7}{-14.6}$ ksi

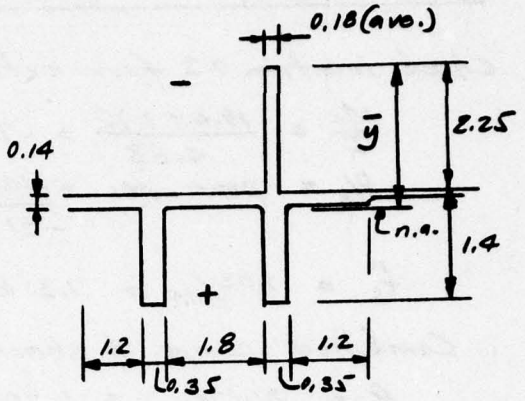

Plan View
(Section @ WL 124.7)

Crippling - (Fig. 22.)

stem (.18) $b/t = 2.25/.18 = 12.5$

$F_{cc} = 5.1/5.33 \times 30 = 28.6$ ksi.

Buckling - ▷ (pg. 372 Fig. 14.25)

$a/b = 16/2.25 = 7.1$

$k = 0.385$

$F_{cr} = kE(t/b)^2 = 0.385 \times 10.4 \times 10^3 (.18/2.25)^2$

$= 25.6$ ksi

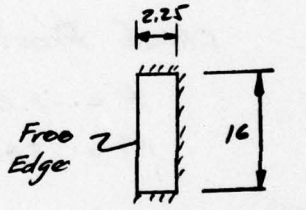

simply supported 3-sides

$M.S._{(comp.)} = \frac{25.6}{14.6} - 1 = \underline{+0.75}$

$P = 19.7^k$ } Bm 135
$M = 5.0^{in-k}$ } see Fig. 21.

Note - Moment is reverse from Bm 136

$P/A = 19.7/1.97 = 10.0$

$\frac{Mc}{I} = \frac{5 \times 2.39}{1.28} = \frac{9.3}{19.3}$ ksi $<$ 40 ksi (F_{tu})

$M.S._{(tension)} = \frac{40}{19.3} - 1 = \underline{high}$

▷ Aircraft structures by D. J. Perry

ENGR.	C. Bacon	11-17-77	REVISED	DATE	CAST BULKHEAD CRITICAL STIFFENER BL 28	CAST Fig. 27
CHECK	BOLLINGER	11-29-77				
APR						
APR					BOEING	48

D1 8007 2070 ORIG. 6/73

J18-047

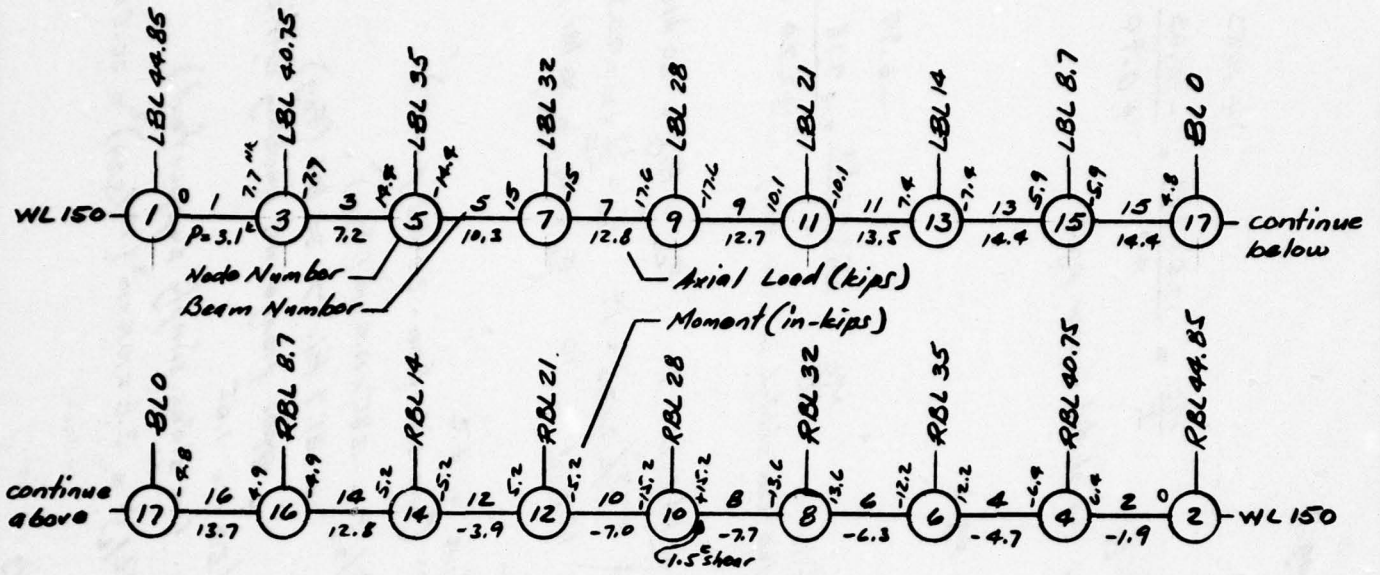

Horizontal Beam @ WL 150

Horizontal Beam @ WL 150
(See Fig. 6 CAST Bulkhead)

Axial loads and moments come from finite element computer model output.

Matl. Prop. for hor. Bm.

F_{tu} = 40 ksi
F_{ty} = 30 ksi
F_{su} = 28 ksi

All values are maximum % ultimate.

Section Properties
A = 1.110 in²
$\bar{y}$ = 2.89
I = 4.7 in⁴

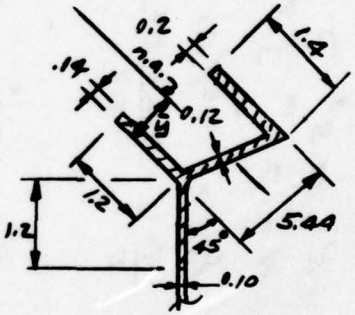

Cross-Section Horizontal Beam

ENGR.	R. Bollinger	11-27-77	REVISED	DATE
CHECK	BOLLINGER	11-29-77		
APR				
APR				

BOEING

Horizontal Beam @ WL 150

CAST Fig. 28

49

D1 9007 2070 ORIG. 6/73

J18-047

Horizontal Beam @ WL 150 (cont'd.)

$P = 12.8^{k}$, $M = 17.6^{in\text{-}k}$ } Bm 7 (see prev. pg.)

$P/A = 12.8/1.11 = 11.53$ $\qquad +11.53$

$\frac{Mc}{I} = \frac{17.6 \times 2.6}{4.7} = 9.74$ $\qquad \frac{Mc}{I} = \frac{17.6 \times 2.89}{4.7} = -10.63$

$+21.27$ ksi $\qquad +0.90$ ksi

(Ten. on top see sketch in prev. pg.)

$P = -7.7^{k}$, $M = 15.2^{in\text{-}k}$ } Bm 8 (see prev. pg.)

$P/A = 7.7/1.11 = -6.94$ $\qquad -6.94$

$\frac{Mc}{I} = \frac{15.2 \times 2.6}{4.7} = -8.41$ $\qquad \frac{Mc}{I} = \frac{15.2 \times 2.89}{4.7} = +9.18$

-15.35 ksi. $\qquad +2.24$ ksi

(comp. on top see sketch in prev. pg.)

Crippling (Fig. 22)

top flange $(t = 0.2)$ $b/t = 1.4/0.2 = 7$ $\qquad F_{cc} = F_{cy} = 30$ ksi

web $(t = 0.12)$ $b/t = 5.27/0.12 \times 2.3 = 19$ $\qquad F_{cc} = \frac{3.7}{5.35} \times 30 = 20.7$ ksi

lower flange $(t = 0.12)$ $b/t = 1.2/0.12 = 10$ $\qquad F_{cc} = F_{cy} = 30$ ksi.

Buckling (▷ pg. 372 Fig. 14.25) –

upper flange – $a/b = 8.7/1.4 = 6.2$

$k = .385$ (one side free – 3 sides pinned)

$F_{cc} = kE(t/b)^2 = .385 \times 10.4 \times 10^3 (.3/1.4)^2$

$= 81.7$ ksi. > 30 ksi. (F_{cy})

upper flange not buckling critical

web – $a/b = 8.7/5.27 = 1.65$

$k = 3.8$ (4 sides simply supported)

$F_{cc} = kE(t/b)^2 = 3.8 \times 10.4 \times 10^3 (.12/5.27)^2 = 20.5$ ksi

▷ Aircraft Structures by Perry

ENGR.	C. Romero	11-22-77	REVISED	DATE	Horizontal Beam @ WL 150	CAST
CHECK	BOLLINGER	11-29-77				Fig. 29
APR.						
APR.					BOEING	50

Horizontal Beam @ WL 150 (cont'd.)

$P = 12.8^{k}$, $M = 17.6^{in\text{-}k}$ } Bm 7 (see prev. pg.)

$P/A = 12.8/1.11 = 11.53$

$\frac{Mc}{I} = \frac{17.6 \times 2.6}{4.7} = 9.74$

21.27 ksi < 40 ksi

upper flange stress, see sketch in Fig. 28

$M.S._{(upper\ flange)} = \frac{40}{21.27} - 1 = \underline{high}$

$P = -7.7^{k}$, $M = 15.2^{in\text{-}k}$ } Bm 8 (see prev. pg.)

$P/A = 7.7/1.11 = -6.94$

$\frac{Mc}{I} = \frac{15.2 \times 2.6}{4.7} = -8.41$

-15.35 ksi { upper flange stress, see sketch in Fig. 28

Web Crippling (Fig. 22) - $b/t = 5.27/0.12 \times 2.3 = 19$ $F_{cc} = \frac{3.7}{5.35} \times 30 = 20.7$ ksi.

Web Buckling compression ([1] pg. 372 Fig. 14.25)

$a/b = 7.0/5.27 = 1.33$

$k = 3.7$ (4 sides simply supported)

$F_{ccr} = kE(t/b)^2 = 3.7 \times 10.4 \times 10^3 (0.12/5.27)^2 = 20.0$ ksi.

Web Buckling Shear (see Figs. 19 & 20)

$t = 0.12$ $F'_{scr} = 27$ ksi

$b/a = 5.27/7.0 = 0.75$ $C_a = 1.44$

$F_{scr(elastic)} = C_a \times F'_{scr} = 1.44 \times 27 = 38.9$ ksi $C_p = 0.56$

$F_{scr} = C_p \times F_{scr(elastic)} = 0.56(38.9) = 21.8$ ksi.

Combined Compression & Shear - $f_s = 1.5/5.27 \times .12 = 2.4$ ksi (Fig. 28, Bm No. 8)

$R_c = f_c/F_{ccr} = 6.94/20 = 0.347$

$R_b = f_b/F_{cu} = 8.41/30 = 0.280$

$R_s = f_s/F_{scr} = 2.4/21.8 = 0.110$

$M.S._{(combined\ stresses)\ web} = \underline{high}$

[1] Aircraft Structures by Perry

ENGR.	[illegible]	11-18-77	REVISED	DATE	Horizontal Beam @ WL 150	CAST
CHECK	BOLLINGER	11-29-77				Fig. 30
APR						
APR					BOEING	51

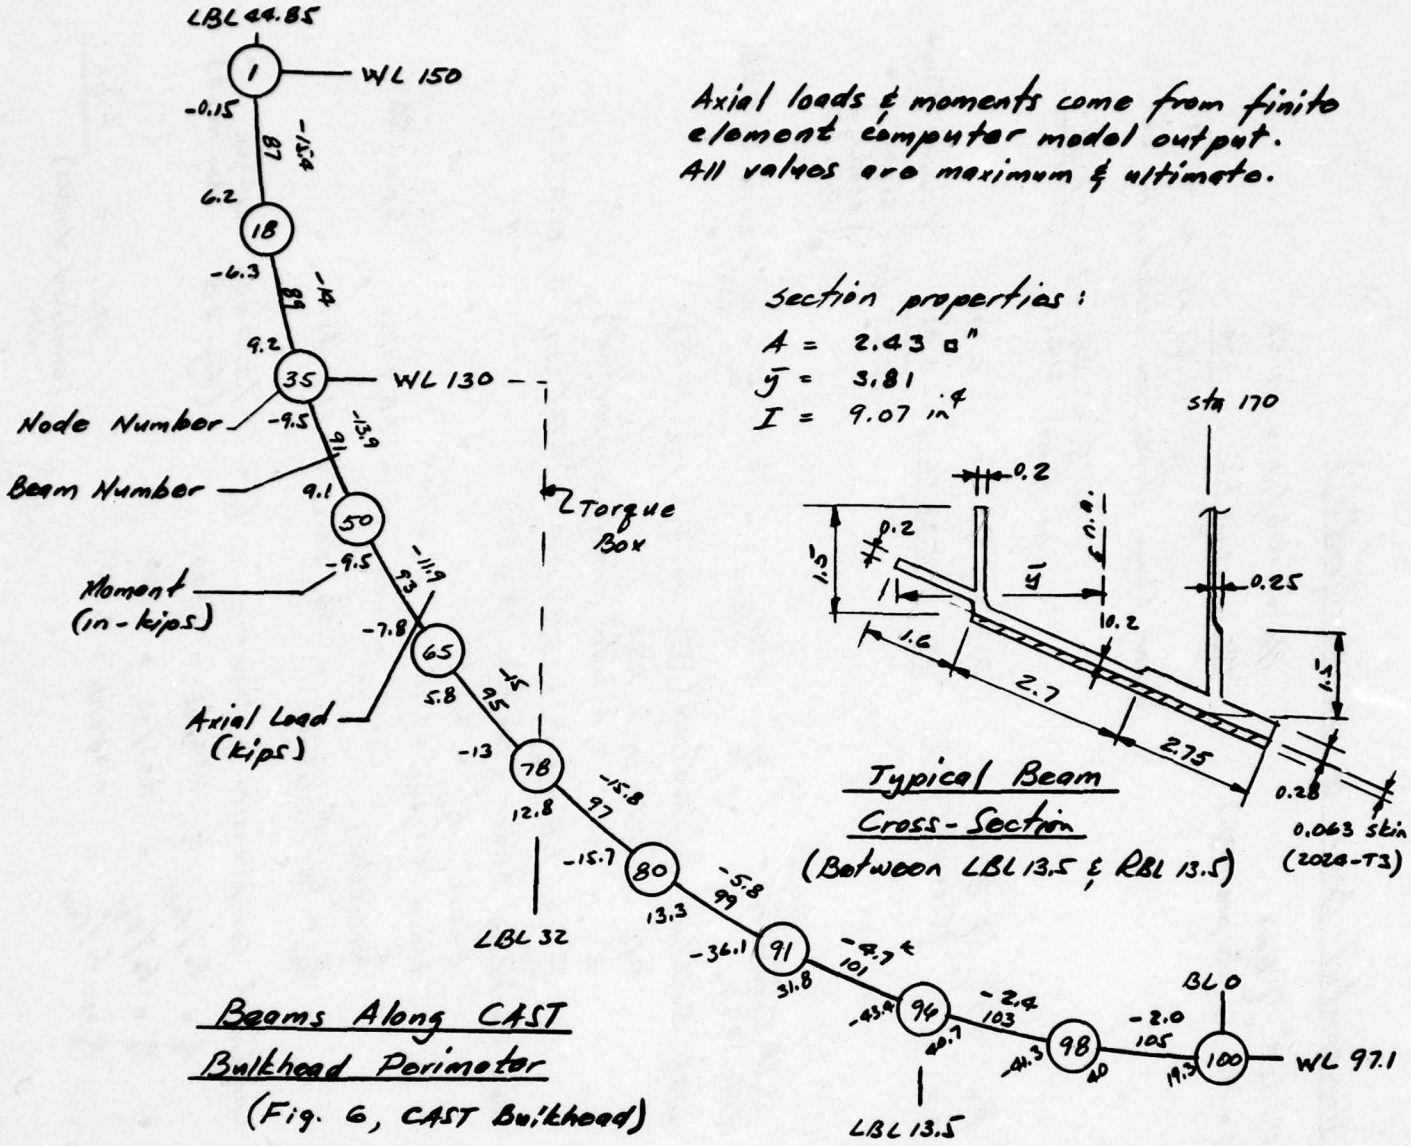

Axial loads & moments come from finite element computer model output.
All values are maximum & ultimate.

Section properties:

$A = 2.43$ □"

$\bar{y} = 3.81$

$I = 9.07$ in^4

Typical Beam Cross-Section
(Between LBL 13.5 & RBL 13.5)

Beams Along CAST Bulkhead Perimeter
(Fig. 6, CAST Bulkhead)

ENGR.					
CHECK	BOLLINGER	11-29-77			
APR					
APR					

CAST - Bulkhead Perimeter Chord

BOEING

CAST

Fig. 31

52

D1 5007 2070 ORIG. 6/73

J18-047

Axial loads and moments come from finite element computer model output.
All values are maximum & ultimate.

Section properties:

$A = 1.98$ in²

$J = 3.87$

$I = 7.32$ in⁴

Typical Beam Cross-Section

(Outboard of LBL 13.5 & RBL 13.5)

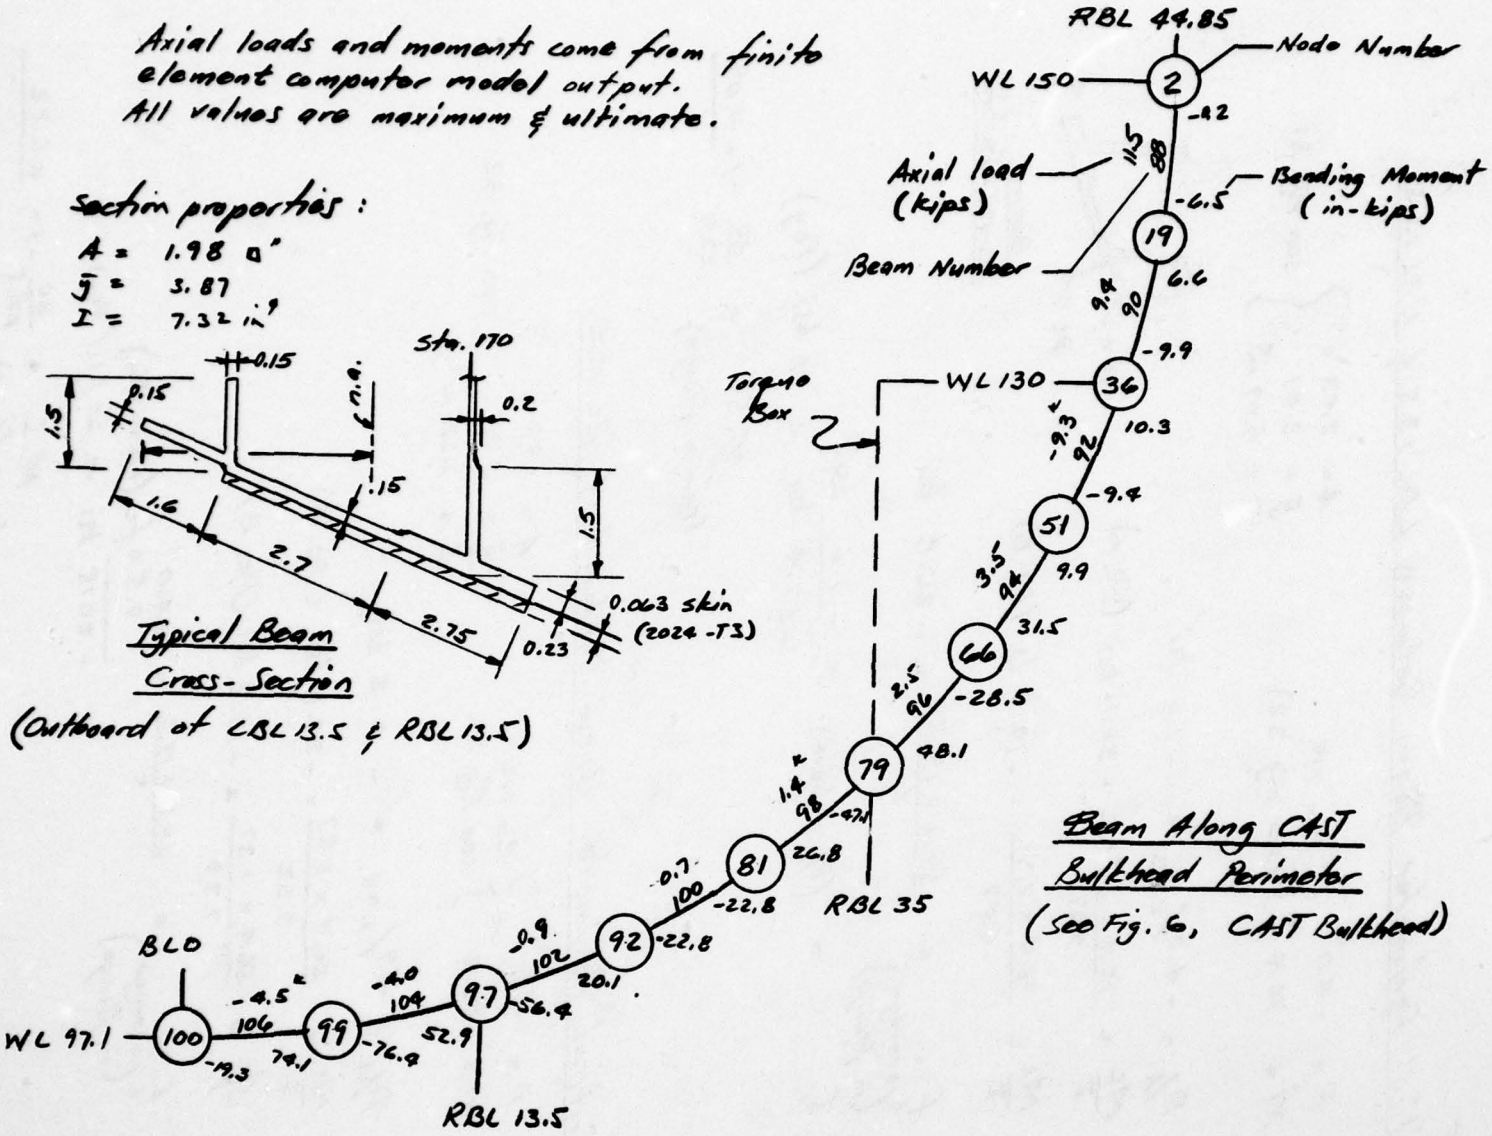

Beam Along CAST Bulkhead Perimeter

(See Fig. 6, CAST Bulkhead)

ENGR.	C. Kassapian	11-29-77	REVISED	DATE
CHECK	BOLLINGER	11-29-77		
APR				
APR				

BOEING

CAST - Bulkhead Perimeter Chord

CAST

Fig. 32

53

D1 8007 2070 ORIG. 6/73

J18-047

Critical Perimeter Beam Between LBL 13.5 & RBL 13.5

$P = -4.0^{k}$, $M = 76.4^{in\text{-}k}$ } Bm 104 (see Fig. 32)

$A = 2.43\ in^2$, $\bar{y} = 3.81$, $I = 9.07\ in^4$ } see Fig. 31.

$P/A = -4.0/2.43 = -1.6$ ksi

$\frac{Mc}{I} = \frac{76.4 \times 3.81}{9.07} = -32.1$ ksi (Pt. A)

$\frac{Mc}{I} = \frac{76.4 \times 2.31}{9.07} = -19.5$ ksi (Pt. B)

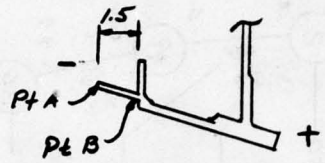

Beam cross-section

$f_{b\,(average\ in\ flange)} = \frac{32.1 + 19.5}{2} = -25.8$ ksi.

$f_c = (P/A\ above) = -1.6$ ksi.

-27.4 ksi $<$ 30 ksi (F_{cy})

M.S. (comp. flange) $= \frac{30}{27.4} - 1 = \underline{+0.09}$

Critical Perimeter Beam Outboard of BL 13.5

$P = -0.9^{k}$, $M = 56.4^{in\text{-}k}$ } Bm 102 see Fig. 32.

$A = 1.98\ 0''$, $\bar{y} = 3.87$, $I = 7.32\ in^4$ } see Fig. 32

$P/A = -0.9/1.98 = -0.5$ ksi.

$\frac{Mc}{I} = \frac{56.4 \times 3.87}{7.32} = -29.8$ ksi (Pt. A)

$\frac{Mc}{I} = \frac{56.4 \times 2.37}{7.32} = -18.3$ ksi (Pt. B)

$f_{b\,(average\ in\ flange)} = \frac{29.8 + 18.3}{2} = -24.0$

$0.5 = f_c$ (above P/A)

-24.5 ksi $<$ 30 ksi (F_{cy})

M.S. (comp. flange) $= \frac{30}{24.5} - 1 = \underline{+0.22}$

CHKD	C. Brown	11-19-77	REVISED	DATE	CAST - Bulkhead Perimeter Chord	CAST
CHKD	BOLLINGER	11-29-77				Fig. 33
					BOEING	54

J18-047

Torque Box @ WL 105 - Landing Gear Door Actuator Support

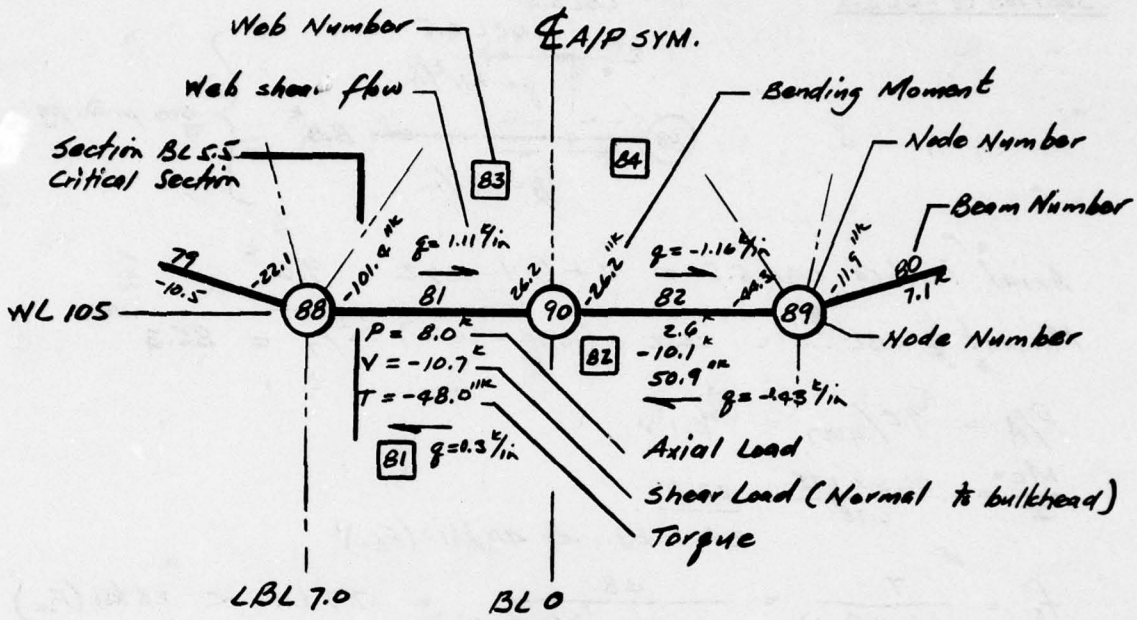

Torque Box Segment of CAST Bulkhead

All values come from finite element computer model output. All values are maximum & ultimate.

Check Section @ LBL 5.5

$A = 4.47\ in^2$

$\bar{y} = 2.34$

$I = 6.78\ in^4$

$J = 9.85$

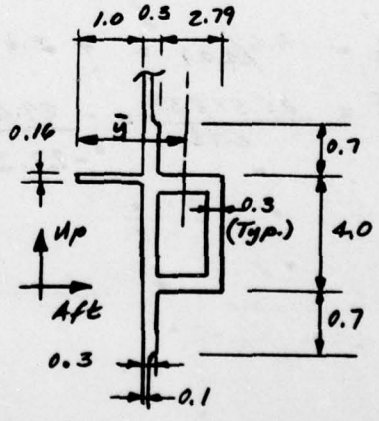

Section @ BL 5.5

ENGR.	C. Roman	11-21-77	REVISED	DATE	Torque Box @ WL 105 L.G. Door Actuator Support	CAST
CHECK	BOLLINGER	11-29-77				Fig. 34
APR						
APR					BOEING	55

Torque Box @ WL 105 (Contd.)

Section @ LBL 5.5

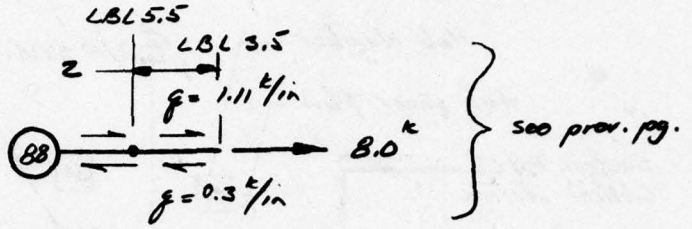

Axial load @ LBL 5.5 = $8 + (1.11 - .3)\,z = 9.6^{k}$

Moment @ LBL 5.5 = $26.2 + (101.4 - 26.2)\,5.5/7 = 85.3^{11k}$

$P/A = 9.6/4.47 = 2.1$

$\frac{Mc}{I} = \frac{85.3 \times 1.75}{6.78} = \frac{22.0}{24.1 \text{ ksi} < 40 \text{ ksi} (F_{tu})}$

$f_s = \frac{T}{2t(a-t)(b-t)} = \frac{48}{2 \times .3 (4-.3)(3.09-.3)} = 7.7 \text{ ksi} < 28 \text{ ksi} (F_{su})$

Combined stresses –

$R_c = 24.1/40 = 0.603$

$R_s = 7.7/28 = 0.275$

M.S. (tension) $= \frac{1}{\sqrt{R_c^2 + R_s^2}} - 1 = \underline{+0.50}$

$P/A = 9.6/4.47 = +2.1$

$\frac{Mc}{I} = \frac{85.3 \times 2.34}{6.78} = -\frac{29.4}{-27.3 \text{ ksi} < 30 \text{ ksi} (F_{cy})}$

M.S. (comp.) $= \frac{30}{27.3} - 1 = \underline{+0.10}$

ENGR.	C. Romero	11-21-77	REVISED	DATE	Torque Box @ WL 105 L.G. Door Actuator Support	CAST Fig. 35
CHECK	BOLLINGER	11-29-77				
APR					BOEING	56
APR						

Lug Back-up Structure @ BL 8.7

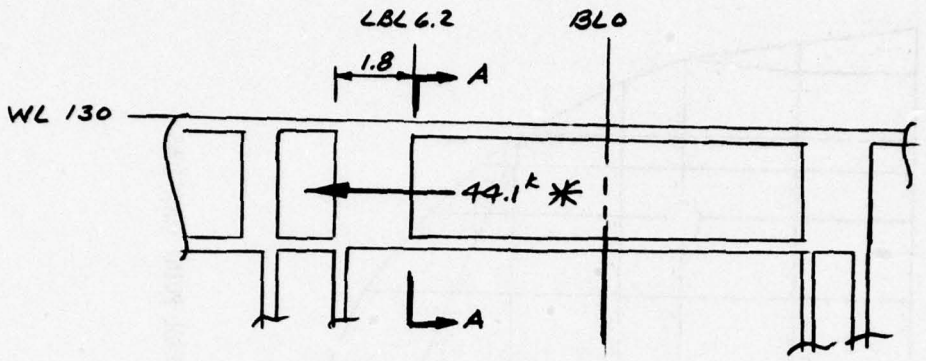

Lug is critical for lateral load

Section properties of A-A -

$A = 4.53$ in²

$\bar{y} = 3.3$

$I = 11.3$ in⁴

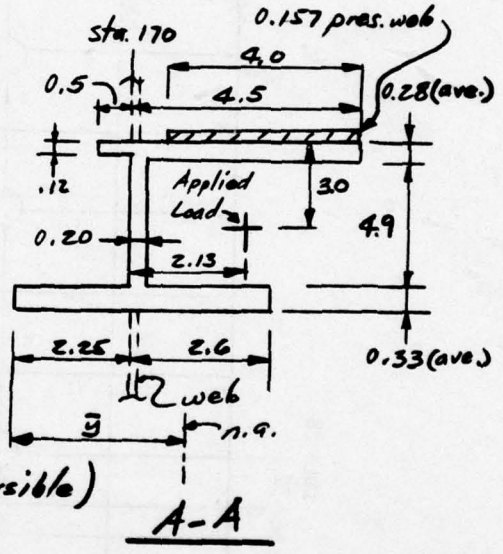

A-A

$M = 44.1\,(4.38 - 3.3) = 47.63$ in-k

$P/A = 44.1/4.53 = +9.7$

$\frac{Mc}{I} = \frac{47.63 \times 3.45}{11.3} = +14.5$

± 24.2 ksi (load is reversible)

$M.S._{(comp.)} = \frac{30}{24.2} - 1 = +0.24$

* Load comes from finite element computer model
Sum V_2 (lateral Bm shear) of Bms 613 & 617

ENGR.	C. Fonseca	11-22-77	REVISED	DATE	Lug Back-up Structure for Lug @ BL 8.7	CAST
CHECK	BOLLINGER	11-29-77				Fig. 36
APR					BOEING	57
APR						

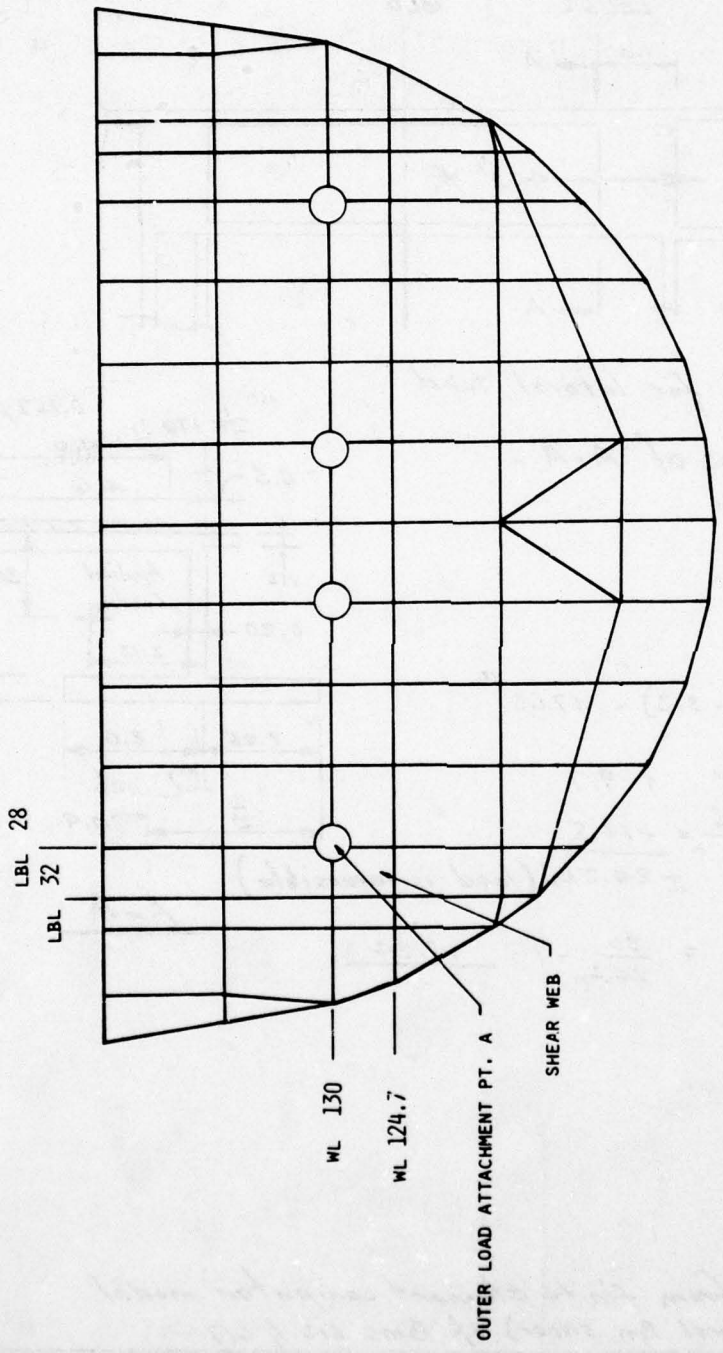

FIGURE 37 DAMAGE TOLERANCE CRITICAL CONTROL POINT LOCATIONS

A third detail/flaw combination consisting of a corner crack at a stiffener on the pressure web was considered; however, finite element analysis showed detail stresses to be uncritical.

According to the requirements of MIL-A-83444, the cast bulkhead is classified as slow crack growth structure and in-service noninspectable.

a. Initial Flaw Assumption

Initial flaw assumptions were made in accordance with MIL-A-83444 requirements for slow crack growth structure:

- o 0.05-inch radius corner flaw at the side of a hole (fig. 38)
- o Semicircular surface flaw with a length (2c) equal to 0.25 inch and a depth (a) equal to 0.125 inch (fig. 39)

b. Material Properties

Crack growth rate (da/dn) for A357 cast aluminum was obtained from fatigue crack growth rate testing using thin compact tension specimens (Test Group A, Specimens ASEN 1 - ASEN 8, ref. 1). A least-squares fit of the data shown in figure 40 was calculated using the Erdogan equation:

$$da/dn = (4.76 \times 10^{-11})\ (D)\ (K_{max})^{4.70}$$

$$\text{where } D = \begin{cases} 0 & ; \quad R > 1 \\ (1-R)^{3.70} & ; \quad 0 \leq R < 1 \\ (1-R/2) & ; \quad -1 < R \leq 0 \\ 1.5 & ; \quad R < -1 \end{cases}$$

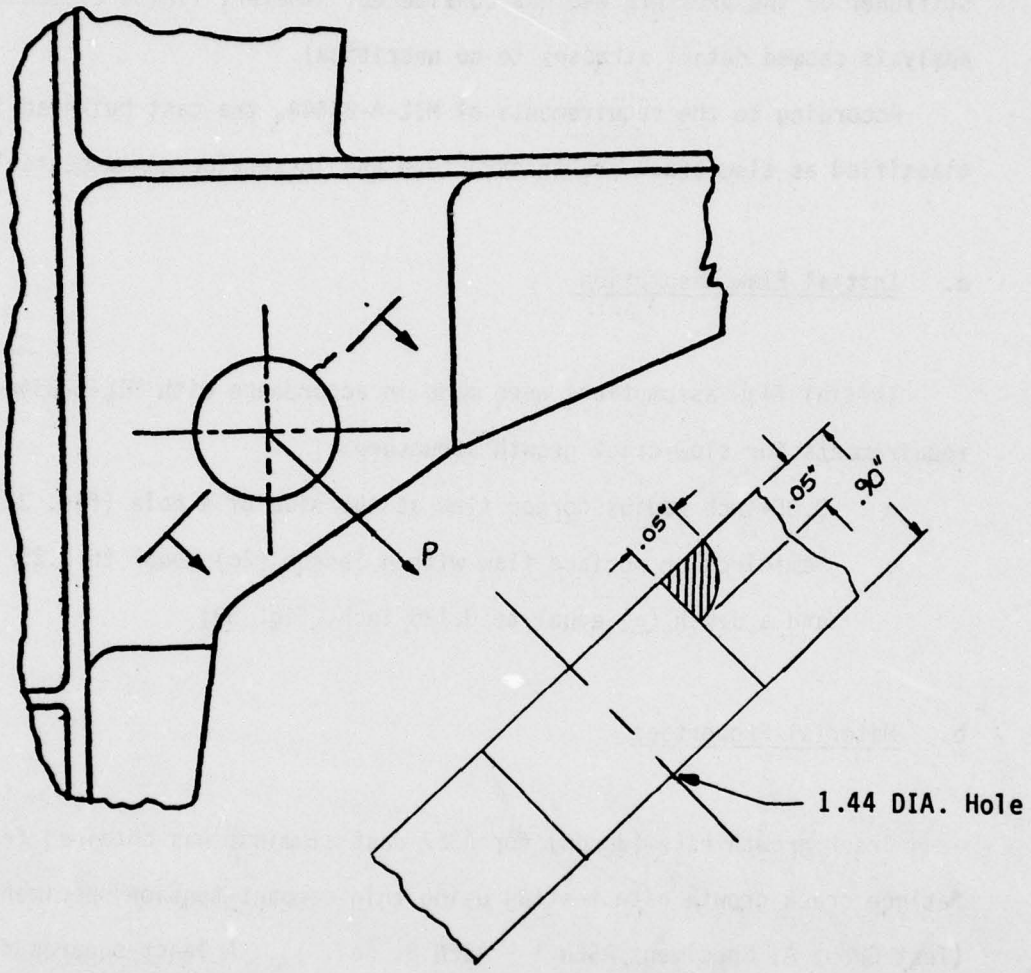

FIGURE 38. LOAD ATTACHMENT POINT A INITIAL FLAW LOCATION

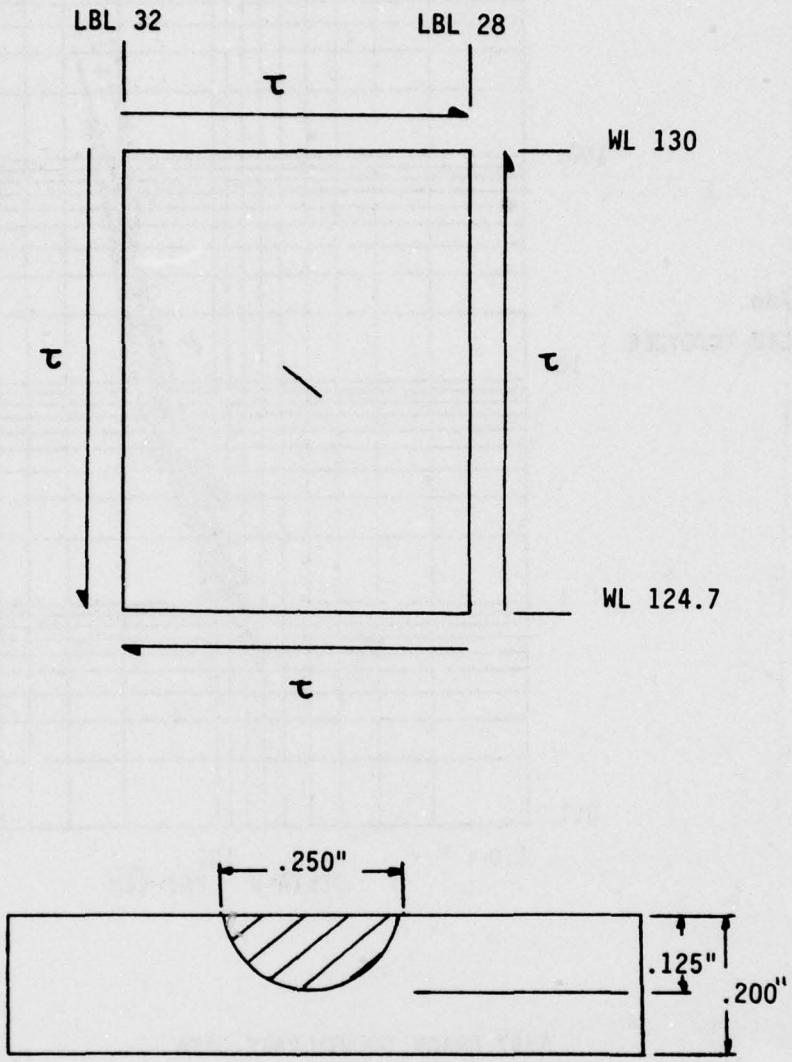

FIGURE 39. SHEAR WEB INITIAL FLAW LOCATION

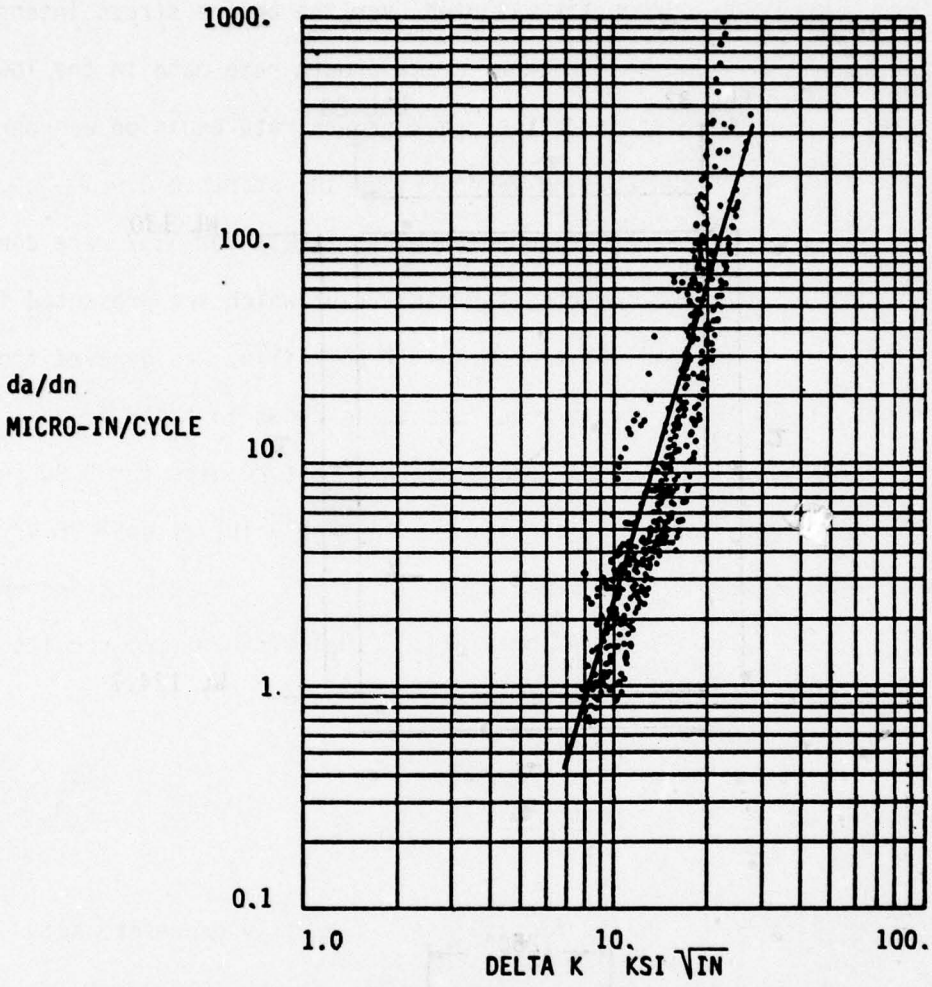

A357 CRACK GROWTH RATE DATA
TEST GROUP A
R = 0.06, LAB AIR
AVERAGE CRACK GROWTH RATE

$$\frac{da}{dn} = (4.76 \times 10^{-11})(1-R)^{3.70}(K_{max})^{4.70}$$

FIGURE 40. A357 ALUMINUM CRACK GROWTH RATE DATA

This least-squares fit was used over the entire stress intensity range (i.e., $K_{th} = 0$) due to a lack of crack growth rate data in the lower ΔK region. The integration of the crack growth rate equation was performed by computer program POWERS7 and is described in reference 2.

Plane strain fracture toughness (K_{IC}) tests for A357 were conducted per ASTM 399-74 requirements, the results of which are presented in reference 1. An average value of $K_{IC} = 17.55$ ksi$\sqrt{\text{in.}}$ was derived from specimens that met K_{IC} validity requirements as shown in table 1.

Plane stress fracture toughness (K_C) test results for 0.20-inch-thick A357 are reported in reference 7. An average value of $K_C = 38.47$ ksi$\sqrt{\text{in.}}$ was derived from the specimens shown in table 2. Specimens for which the final crack length exceeded one-third of the width of the specimens were not used in deriving the average value of K_C.

c. Stress Intensity Factor Solution

The stress intensity factor, K, is generally expressed as:

$$K = \sigma \cdot \sqrt{\pi a} \cdot Y$$

The correction factor for radius corner flaws, Y_{CF}, is the result of a number of correction factors found in reference 3 for the case of a corner radius flaw originating at a loaded hole as shown in figure 38.

The applied stress, σ, is the bearing stress resulting from the applied load through the pin and the clevis geometry.

TABLE 1. K_{IC} PLANE STRAIN FRACTURE TOUGHNESS DATA

SPECIMEN IDENTIFICATION	* K_{IC} (KSI $\sqrt{IN.}$)
ACT 3-2	16.6
ACT 4-2	16.0
ACT 7-1	19.4
ACT 8-1	18.2

* Specimens meet ASTM E399-74 validity requirements

$$(K_{IC})_{AVG} = \frac{70.20}{4} = 17.55 \text{ KSI}\sqrt{\text{IN.}}$$

TABLE 2. K_c PLANE STRESS FRACTURE TOUGHNESS DATA

SPECIMEN IDENTIFICATION	K_{APP} (KSI $\sqrt{IN.}$)
ACC 1-1	36.11
ACC 1-2	34.73
ACC 2-1	41.35
ACC 2-2	45.75
ACC 3-2	42.90
ACC 4-1	35.90
ACC 4-2	35.23
ACC 5-1	45.22
ACC 6-2	45.02
ACC 7-1	49.38
ACC 7-2	35.01
ACC 8-1	29.67
ACC 8-2	23.87

$$(Kc)_{AVG} = \frac{500.14}{13} = 38.14 \quad KSI\sqrt{IN.}$$

The stress intensity solution used for the corner radius flaw at a pin-loaded hole is:

$$K = \sigma \cdot \sqrt{\pi a} \cdot Y_{CF}$$

where $Y_{CF} = 1/\sqrt{Q} \cdot M_F \cdot M_B \cdot F_6 \cdot [\cos^2\beta + a^2/c^2 \sin^2\beta]^{1/4}$

$$\sqrt{\frac{2r + \pi ac/4t}{2r + 2\pi ac/4t}} \qquad \text{(ref. 3)}$$

The correction factor used for the surface flaw case, Y_{SF}, is derived from reference 4.

The surface flaw is oriented such that the principal tensile stresses acting on the web are perpendicular to the crack.

The stress intensity solution used for the surface flaw is:

$$K = \sigma \cdot \sqrt{\pi a} \cdot Y_{SF}$$

where $Y_{SF} = 1/\sqrt{Q} \cdot M_B \cdot [\cos^2\beta + a^2/c^2 \sin^2\beta]^{1/4}$ (ref. 4)

and $$\sigma = \frac{\sigma_x + \sigma_y}{2} \pm \sqrt{\frac{\sigma_x + \sigma_y}{2} + txy^2}$$

d. Loads

The repeated external loads noted in reference 2 are used for the analyses. The stresses applied are representative of the design usage as given by the mission mix of reference 2. Local stresses for both details were derived from unit load solutions based on finite element analysis of the bulkhead. Analysis stresses for attachment point A and shear web details are presented in appendix A and appendix B, respectively.

MIL-A-83444 requires that the assumed initial damage of in-service noninspectable slow crack growth structure shall not grow to critical size in two design service lifetimes. It also specifies that the structure must be capable of withstanding a residual strength load, P_{LT}, which is the maximum average internal member load that will occur once in 20 lifetimes. The residual strength load to be applied to the bulkhead is the design limit load for the Boeing Side Load condition and is given in reference 5.

e. Results

Damage tolerance analysis results presented in table 3 demonstrate that the requirements specified in MIL-A-83444 for in-service noninspectable slow crack growth structure were met for both details:

AD-A057 422 BOEING AEROSPACE CO SEATTLE WASH F/G 1/3
COST ALUMINUM STRUCTURES TECHNOLOGY, PHASE III (CAST).(U)
JAN 78 D GOEHLER F33615-76-C-3111
UNCLASSIFIED D180-22807-1 AFFDL-TR-78-7 NL

2 OF 2
ADA
057422

END
DATE
FILMED
9-78
DDC

TABLE 3 FLAW GROWTH SUMMARY FOR BULKHEAD DETAILS

DETAIL	$a_{initial}$	$a_{1\ life}$*	$a_{2\ lives}$*	$a_{critical}$**
Load Attachment Point A	0.05"	0.050"	0.050"	0.10"
Shear Web (LBL 28-32/ WL 124.7-130)	0.125"	0.125"	0.125"	4.39"

* One serivce life consists of 1516 applications of the mission mix block

** $a_{critical}$ is determined using design limit load.

- Outer load attachment point A -- Preliminary analyses reported in reference 6 showed that the initial flaw grew to 0.10 inch in two service lives. This preliminary analysis assumed the attachment point to be loaded in uniform tension. A more realistic pin loading was assumed in the current analysis, resulting in smaller stress intensity factors. In addition, the assumed crack growth rate used for analysis in reference 6 is significantly faster than that derived from test data. The combined effect of smaller K values and slow crack growth rate results in less crack growth than shown in the preliminary analysis (ref. 6). In two service lives, the corner radius flaw assumed at load attachment point A grows from 0.05 inch to 0.05036 inch. Critical crack length for this detail based on P_{LT} = 25.59 ksi and K_{IC} = 17.55 ksi$\sqrt{in.}$ was calculated to be 0.10 inch.
- Shear web between LBL 28-LBL 32 and WL 124.7-WL 130 -- The surface flaw grows from an initial value of a = 0.125 inch, 2c = 0.250 inch to a = 0.12505 inch, 2c = 0.2501 inch in two service lifetimes. Critical crack length for this detail based on P_{LT} = 10.36 ksi and K_C = 38.47 ksi$\sqrt{in.}$ was found to be 4.39 inches.

A357 fatigue crack growth test results showed that little growth occurred below a stress intensity level of 10 ksi$\sqrt{in.}$ The maximum spectrum stress intensity, K_{max}, in the damage tolerance analysis for the 0.05-inch radius corner flaw at attachment point A is 7.25 ksi$\sqrt{in.}$, while K_{max} for the shear web surface flaw (2c = 0.250 inch, a = 0.125 inch) is 4.55 ksi$\sqrt{in.}$ The maximum stress intensity that occurs each flight in the spectrum for the 0.05-inch radius corner flaw at attachment point A is 2.32 ksi$\sqrt{in.}$, whereas for the shear web the maximum stress intensity that occurs every flight is 1.41 ksi$\sqrt{in.}$ Therefore, little crack growth would be expected for either detail since the spectrum stress intensities for cracks on the order of MIL-A-83444 assumed initial flaw sizes are well below 10 ksi$\sqrt{in.}$

3. SENSITIVITY STUDIES

Sensitivity studies were performed to identify the sensitivity of crack growth life predictions to material properties, aircraft usage, and the initial flaw size assumed to exist. The details used for the studies are those selected for the damage tolerance analysis (sec. III.2, fig. 37):

- Outer load attachment point A
- Shear web located between LBL 28-LBL 32 and WL 124.7-WL 130.

The results of these studies are presented below.

a. Sensitivity to Material Properties

The sensitivity of the analysis results to the variability of the material properties was established by using upper bound and average crack growth rate (fig. 41) and average and lower bound fracture toughness properties (table 4) to perform crack growth analyses for each bulkhead detail. The loads spectrum representing the equivalence of typical usage was used. The results discussed below are shown in table 4.

- Load attachment point A -- The corner radius flaw grows from 0.05 inch to 0.05933 inch in two service liftimes using upper bound crack growth rate data. A critical crack length of 0.08 inch was calculated using a lower bound K_{IC} = 16.00 ksi$\sqrt{in.}$ and P_{LT} = 25.59 ksi (sec. III.2.e).
- Shear web -- The initial surface flaw (2c = 0.250 inch, a = 0.125 inch) grows to a crack depth of 0.13201 inch in two service lifetimes using upper bound crack growth rate data. The critical crack length was determined to be 1.69 inches for a through-the-thickness crack using a lower bound K_C = 23.87 ksi$\sqrt{in.}$ and P_{LT} = 10.36 ksi (sec. III.2.e).

The use of upper bound crack growth rate data had little effect on the crack growth results for either detail, while lower bound fracture toughness properties caused the critical crack lengths of the details to be smaller. Thus, MIL-A-83444 requirements can still be met using upper bound crack growth data and lower bound fracture toughness properties.

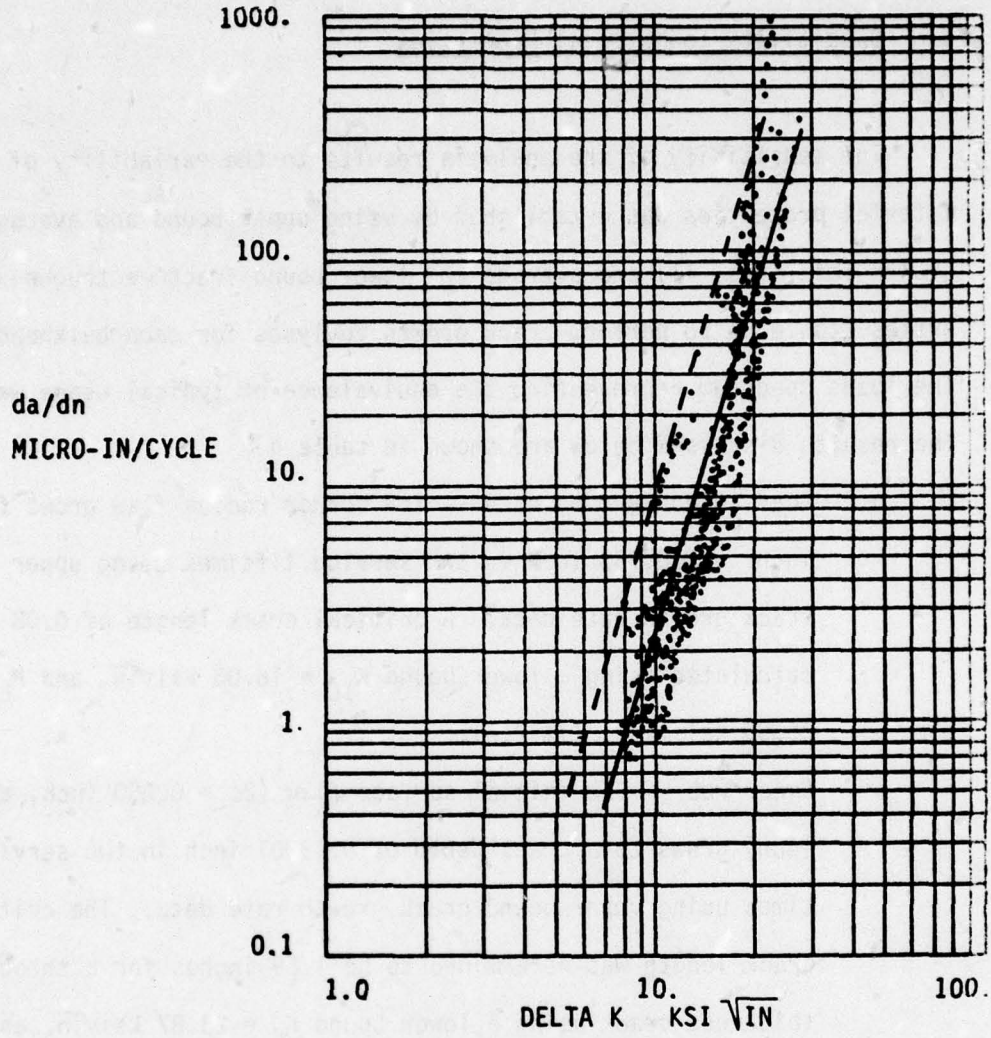

TEST GROUP A

R = 0.06, LAB AIR

AVERAGE CRACK GROWTH RATE

$$\text{——} \quad \frac{da}{dn} = (4.76 \times 10^{-11})(1-R)^{3.70}(K_{max})^{4.70}$$

UPPER BOUND CRACK GROWTH RATE

$$\text{-----} \quad \frac{da}{dn} = (1.53 \times 10^{-10})(1-R)^{3.70}(K_{max})^{4.70}$$

FIGURE 41 A357 CRACK GROWTH RATE DATA

TABLE 4. MATERIAL PROPERTIES SENSITIVITY STUDIES

DETAIL	MATERIAL DATA		$a_{initial}$	$a_{1\ life}$	$a_{2\ lives}$	$a_{critical}$
	da/dn*	K_{IC}**				
LOAD ATTACHMENT POINT A (CORNER FLAW AT A HOLE)	AVERAGE DATA	AVERAGE DATA	0.05"	0.050"	0.050"	0.10"
	UPPER BOUND DATA	LOWER BOUND DATA	0.05"	0.050"	0.050"	0.08"
SHEAR WEB (SURFACE FLAW)	AVERAGE DATA	AVERAGE DATA	0.125"	0.125"	0.125"	4.39"
	UPPER BOUND DATA	LOWER BOUND DATA	0.125"	0.125"	0.125"	1.69"

*AVERAGE DATA $C = 4.76 \times 10^{-11}$, $N = 3.70$, $M = 4.70$

UPPER BOUND DATA $C = 1.53 \times 10^{-10}$, $N = 3.70$, $M = 4.70$

**LOAD ATTACHMENT POINT A: AVERAGE DATA $K_{IC} = 17.55$ KSI $\sqrt{IN}$

(t = 0.09") LOWER BOUND DATA $K_{IC} = 16.00$ KSI $\sqrt{IN}$

SHEAR WEB: AVERAGE DATA $K_C = 38.47$ KSI $\sqrt{IN}$

(t = 0.20") LOWER BOUND DATA $K_C = 23.87$ KSI $\sqrt{IN}$

b. Sensitivity to Aircraft Usage

Crack growth analyses were performed for the two bulkhead details using average crack growth data (fig. 41) and fracture toughness properties (sec. III.2.b). Loads spectra representing aircraft usage which is more damaging than typical usage were used for this study. This spectrum consists of a mission mix containing three more STOL flights and three fewer CTOL flights than typical usage as shown in table 5. One service life of typical usage would contain 15,160 CTOL and 9,096 STOL flights, whereas the usage defined in this study contains 10,612 CTOL and 13,644 STOL flights in each lifetime. Typical usage is defined by the loads spectrum in appendix C of reference 2. Studies concerning spectra that are less damaging than normal usage were not conducted due to the small amount of crack growth produced by the typical usage loads spectrum.

The results of the aircraft usage sensitivity studies are presented in table 6. In two design service lifetimes, the radius corner flaw at load attachment point A grew from 0.05 inch to 0.05048 inch, whereas the shear web surface flaw grew from a surface crack length (2c) of 0.250 inch to 0.2512 inch. From these results, it is evident that the change in mission mix for this study had little effect on the crack growth.

c. Sensitivity to Initial Flaw Assumption

Crack growth analyses were performed assuming larger initial flaw sizes than defined in MIL-A-83444. Average material properties (sec. III.2.b and typical aircraft usage were assumed.

TABLE 5 MISSION MIX MAKE-UP

FLIGHT TYPE	TYPICAL USAGE	STUDY USAGE
1 (CTOL)	1	1
2 (CTOL)	4	1
3 (STOL)	3	3
4 (CTOL)	5	5
5 (STOL)	3	6
FLIGHTS / BLOCK	16	16

TABLE 6 AIRCRAFT USAGE SENSITIVITY STUDIES

DETAIL	SPECTRUM MAKE-UP	a initial	a 1 life	a 2 lives
LOAD ATTACHMENT POINT A (CORNER FLAW AT A HOLE)	TYPICAL USAGE	0.05"	0.050"	0.050"
	STUDY USAGE	0.05"	0.050"	0.050"
SHEAR WEB (SURFACE FLAW)	TYPICAL USAGE	0.125"	0.125"	0.125"
	STUDY USAGE	0.125"	0.125"	0.125"

The results of this study are presented in table 7. An initial corner radius flaw of 0.06 inch was assumed for outer load attachment point A. This grew to a flaw size of 0.06051 inch in two service lives. Additionally, when an initial flaw size of 0.080 inch was assumed, the crack grew to 0.090 inch in two service lifetimes, still below the 0.10-inch critical crack length. The shear web surface flaw was assumed to begin at a depth (a) of 0.150 inch and a surface length (2c) of 0.300 inch. After two service lifetimes of typical aircraft usage, the crack grew to a depth of 0.15008 inch and a surface length of 0.30016 inch. Analysis assuming an initial through-the-thickness flaw length of 1.35 inches resulted in the crack growing to a length of 3.00 inches in two lives.

From these analyses, it is evident that an equivalent initial flaw size that is much larger than that required by MIL-A-83444 will not grow to critical crack size in two service lifetimes for either detail.

4. DURABILITY ANALYSIS

Durability analyses were performed for the details selected for the damage tolerance analysis:

- Outer load attachment point A
- Shear web located between LBL 28-LBL 32 and WL 124.7-WL 130

Detail locations are presented in figure 37. The loads acting on these two details were calculated from external loads using unit load solutions derived from finite element analysis results. The Boeing Durability Method is used for all durability calculations (ref. 2).

TABLE 7. INITIAL FLAW ASSUMPTION SENSITIVITY STUDIES

DETAIL	$a_{initial}$	$a_{1\ life}$	$a_{2\ lives}$
LOAD ATTACHMENT POINT A (CORNER FLAW AT A HOLE)	0.05"	0.050"	0.050"
	0.06"	0.060"	0.060"
	0.080"	0.083"	0.090"
SHEAR WEB (SURFACE FLAW)	0.125"	0.125"	0.125"
	0.150"	0.150"	0.150"
	1.350"	1.985"	3.00"

a. Detail Design S-N Curves

The S-N curves for A357 are developed from fatigue test data for both smooth and open-hole fatigue test specimens as shown in figure 42. The design S-n curves for each detail are derived from test data by applying appropriate factors to achieve 95% confidence and 95% reliability. Detail design S-N curves for smooth and open-hole specimens are presented in figures 43 and 44, respectively.

Detail design S-N curves are expressed by two parameters: a detail fatigue rating, DFR, and slope ratio, S. The slope ratio, S, is generally constant at 2.0 for aluminum alloys. The geometric severity of a particular detail considering its fatigue performance is therefore expressed by the DFR.

For a clevis or lug detail, the DFR is derived from:

$$DFR = DFR_{BASE} \cdot A \cdot L_s \cdot L_d \cdot L$$

The DFR_{BASE} value accounts for the particular geometry of the clevis or lug. Since the DFR_{BASE} charts are presently derived for wrought aluminum alloys, the factor A accounts for the effect of the casting alloy. The factor A is derived as the ratio:

$$A = \frac{DFR\ (OPEN\ HOLE\ A357)}{DFR\ (OPEN\ HOLE\ 2024)}$$

where DFR (open hole A357) is as shown on figure 44 and DFR (open hole 2024) is obtained from durability design charts.

Therefore,

$$A = \frac{11.0}{16.5} = 0.67$$

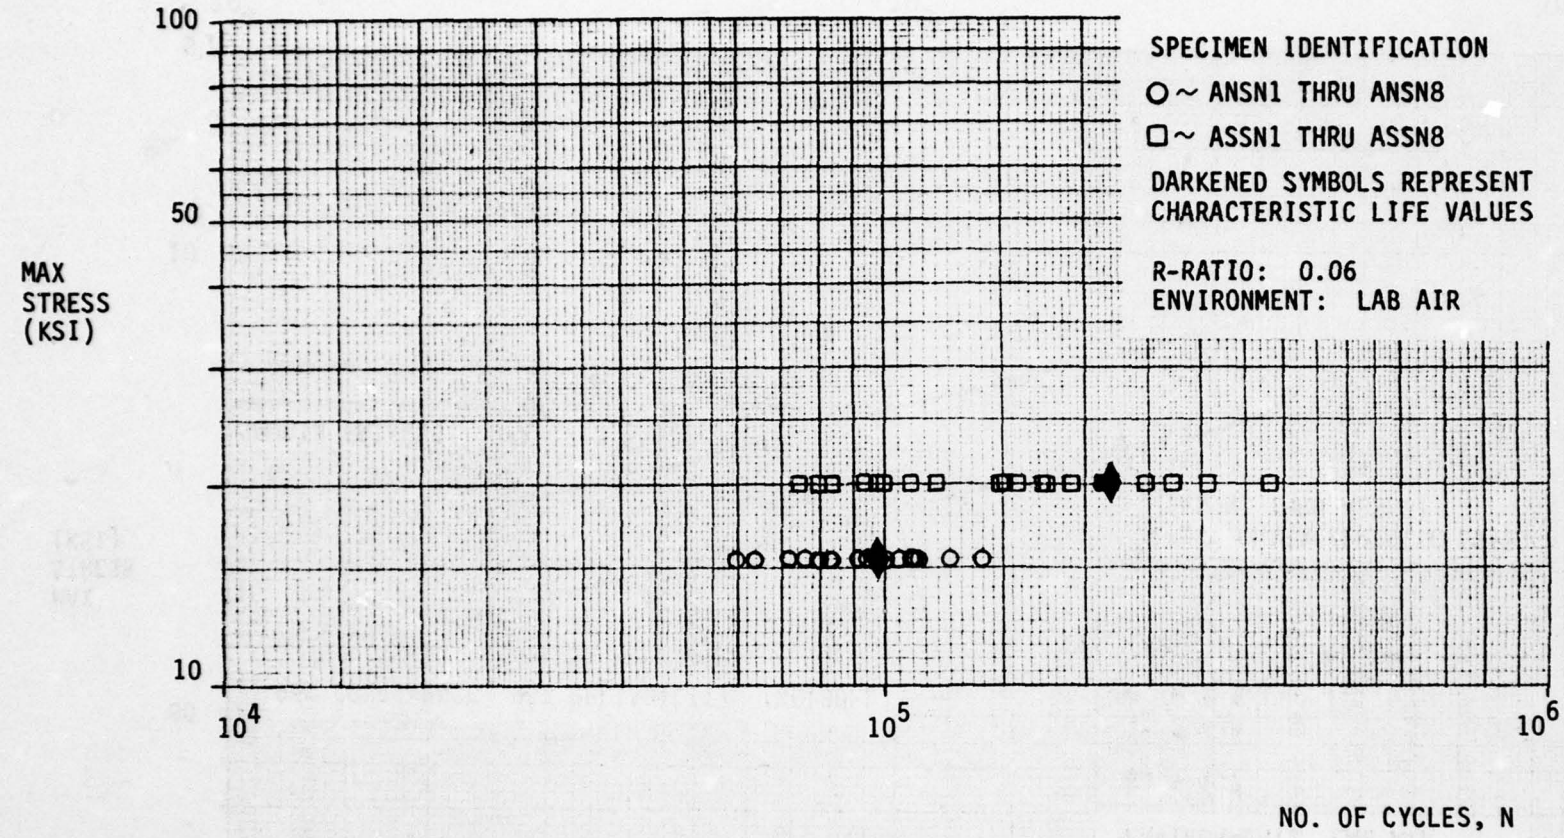

FIGURE 42. A357 S-N DATA FOR SMOOTH AND OPEN HOLE SPECIMENS

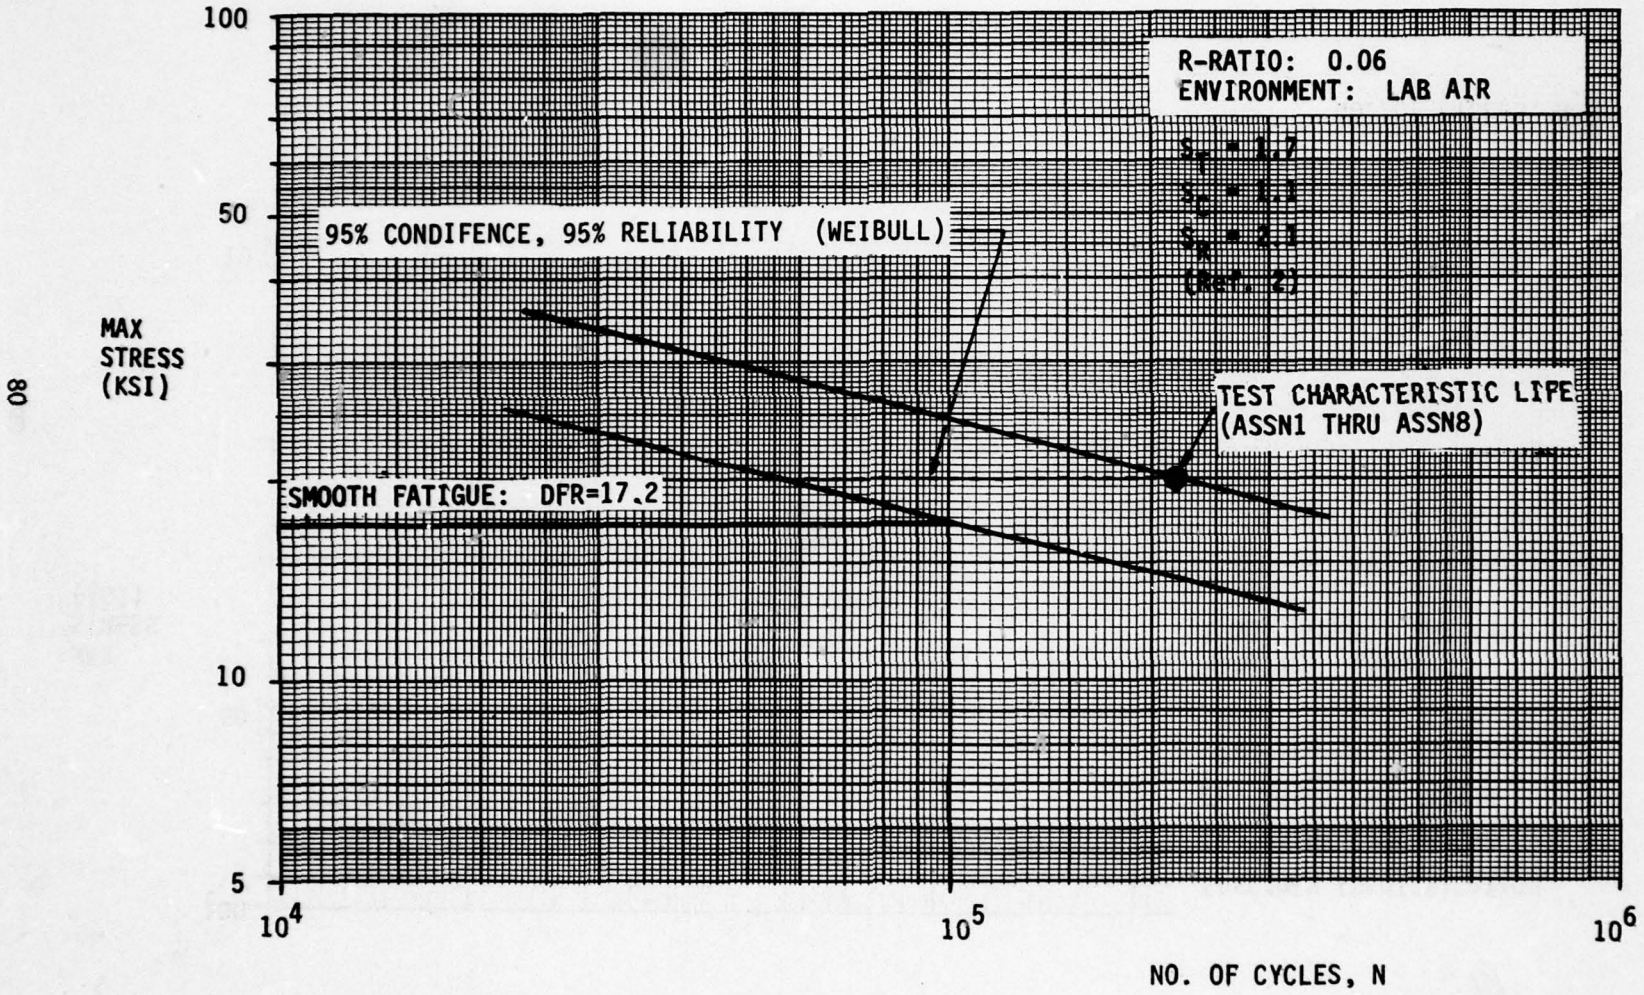

FIGURE 43. DETAIL DESIGN S-N CURVES FOR SMOOTH FATIGUE SPECIMENS

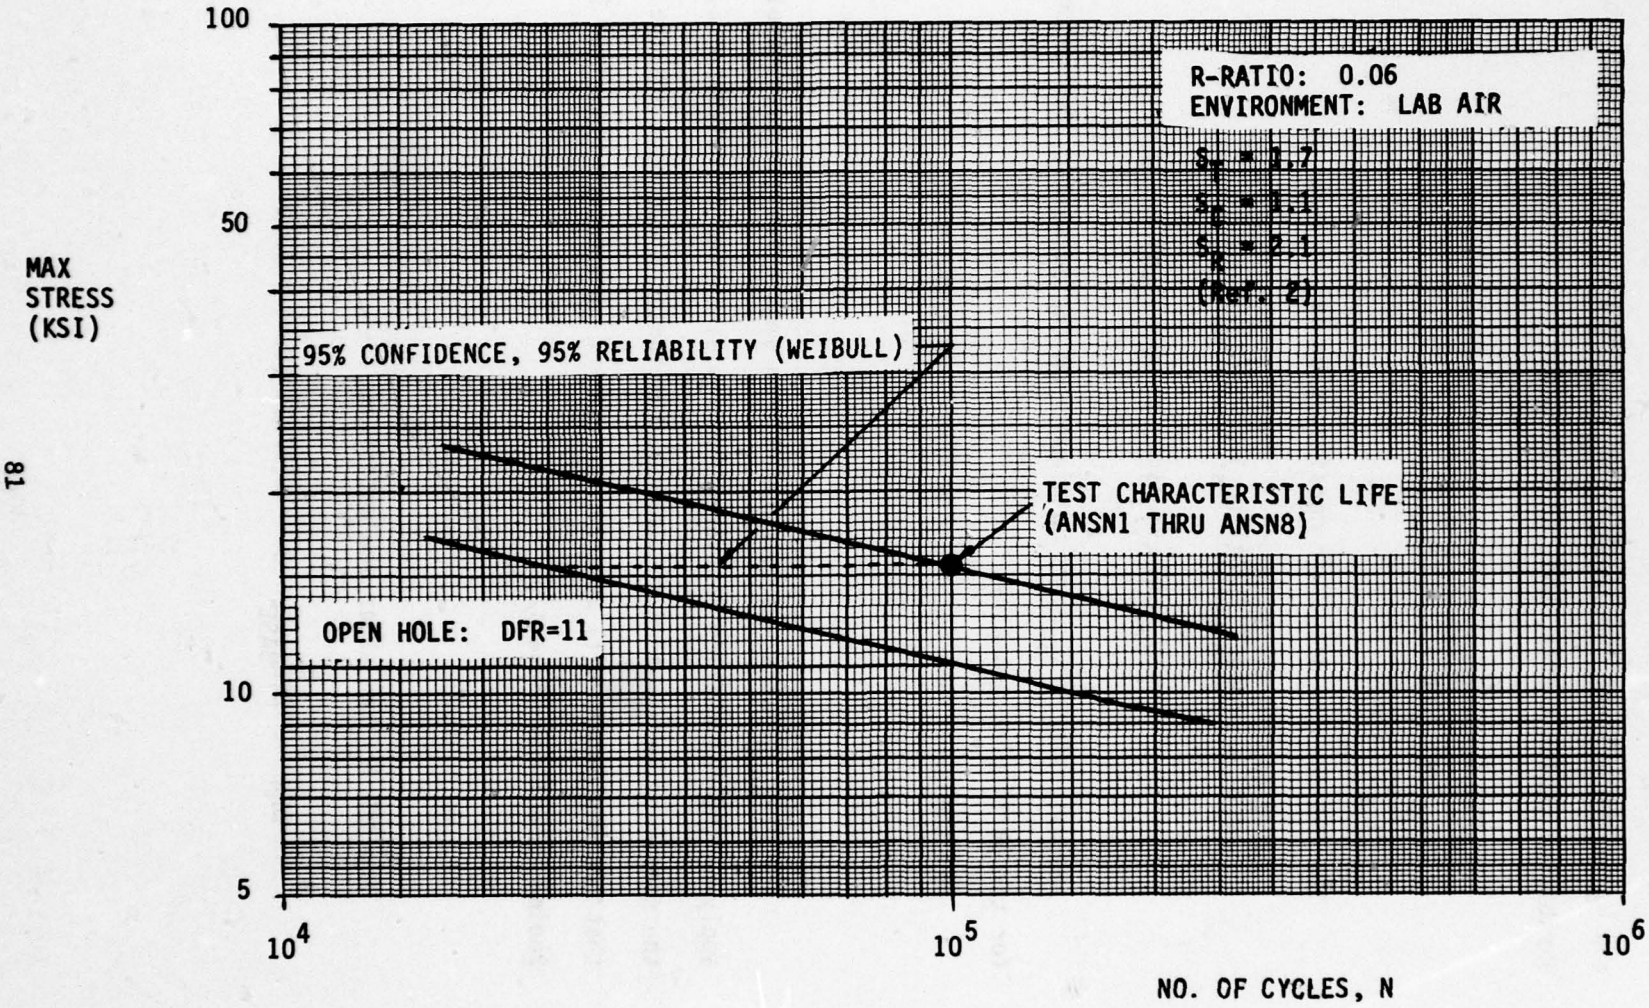

FIGURE 44. DETAIL DESIGN S-N CURVES FOR OPEN HOLE SPECIMENS

L_s and L_d represent the geometric size and shape factor, respectively, and L_θ is the oblique load factor. L_s, L_d, and L_θ are obtained from the durability design charts, and for this case:

$$L_s = 1.00$$

$$L_d = 1.06$$

$$L_\theta = 1.00$$

The DFR for the detail in consideration is

$$DFR = (DFR_{BASE})\ (A)\ (L_s)\ (L_d)\ (L_\theta)$$

$$= (12.80)\ (0.67)\ (1.0)\ (1.06)\ (1.0) = 9.1$$

The value for DFR_{BASE} is obtained from the durability design charts for the particular geometry.

For the shear web detail, the DFR is derived from:

$$DFR = DFR_{BASE} \cdot B$$

The DFR_{BASE} value was calculated from smooth fatigue test results applying the reliability considerations as discussed in reference 2. Since the specimens were loaded in tension, the factor B accounts for the fact that the web detail will be loaded in shear. The factor B is from the Boeing Durability Manual:

$$B = 0.7$$

The DFR for the shear web detail is:

$$DFR = DFR_{BASE} \cdot B = (17.2)\ (0.7) = 12.0$$

b. Economic Life

The economic life of the cast bulkhead is predicted for the design usage as represented by the mission mix noted in reference 2. The relative damage due to the five different flights within the mission mix consisting of 16 total flights is calculated and summarized for both the load attachment point A and shear web details in tables 8 and 9, respectively.

The relative damage of each flight is the sum of the damages of the individual stress excursions applied during each flight. The relative damages for the individual stress cycles are calculated from the S-N curves by:

$$\text{relative damage} = \frac{100{,}000}{N_{S\text{-}N}} \cdot n_{applied}$$

The GAG damage ratio is calculated from

$$\text{GAG damage ratio} = \frac{\text{relative damage GAG cycle}}{\text{relative damage total flight}}$$

For load attachment point A, the average GAG cycle was determined to be:

$$(f_{max})_{GAG} = 7.88 \text{ ksi}$$

$$(f_{min})_{GAG} = 0.0 \text{ ksi}$$

The average relative damage of this GAG cycle is established as:

relative GAG damage = 0.361 (ref. table 8)

The average GAG damage ratio for this detail is:

0.361/1.242 = 0.29

TABLE 8. LOAD ATTACHMENT POINT A--RELATIVE DAMAGE

FLIGHT TYPE	No. of FLIGHTS	DAMAGE EACH FLIGHT [1]	TOTAL DAMAGE	GAG DAMAGE EACH FLIGHT
1	1	1.055	1.055	0.542
2	4	1.055	4.220	0.542
3	3	1.424	4.272	0.279
4	5	0.629	3.145	0.279
5	3	2.394	7.182	0.279
	16		19.874	
average damage per flight = 1.242				
average GAG damage = 0.361				

[1] based on DFR = 16

TABLE 9. SHEAR WEB--RELATIVE DAMAGE

FLIGHT TYPE	NO. OF FLIGHTS	DAMAGE EACH FLIGHT [1]	TOTAL DAMAGE	GAG DAMAGE EACH FLIGHT
1	1	0.0227	0.0227	0.0178
2	4	0.0227	0.0908	0.0178
3	3	0.0414	0.1242	0.0281
4	5	0.0164	0.0820	0.0123
5	3	0.0526	0.1578	0.0281
	16		0.04775	
average damage per flight = 0.0298				
average GAG damage = 0.0220				

[1] based on DFR = 16

For the life predictions, the GAG cycle will be used in place of the variable amplitude flight stress excursions. For that purpose, an equivalent number of cycles for the GAG excursions must be established as the life goal. The design service life of the bulkhead is 25,000 hours. Using the average duration for one flight of 1.03 hours, the number of flights is 24,272. The equivalent number of GAG cycles for the life requirement is:

$$N_{equ} = \frac{(N_{FLIGHTS})\ (FRF)}{\text{GAG damage ratio}}$$

$$N_{equ} = \frac{(24272)\ (1.5)}{0.2907} = 125{,}243 \text{ cycles}$$

An additional fatigue reliability factor, FRF, is applied in accordance with the Boeing Durability Method. The factor is mainly a function of the location of the analysis detail on the airplane.

Using the detail design curve defined by a DFR = 9.1, f_{max} = 7.88 ksi, and R = 0 for the clevis detail results in a life prediction expressed in terms of GAG cycles of 135,000 cycles. In terms of hours, the economic life is predicted as:

$$\text{life} = (25000)\ \frac{(135{,}000)}{(125{,}243)} = 26{,}948 \text{ hours}$$

The economic life therefore exceeds the design life by 8%. In terms of stresses, the fatigue margin is:

$$FM = \frac{F_{max}}{f_{max}} - 1 = \frac{8.25}{7.88} - 1 = 0.037$$

where F_{max} is the maximum allowable GAG stress.

The shear web analysis was performed in the same manner. The GAG cycle was determined to be:

$$(f_{max})_{GAG} = 2.85 \text{ ksi}$$

$$(f_{min})_{GAG} = -3.16 \text{ ksi}$$

The average relative damage for this GAG cycle as shown in table 9 is:

$$\text{relative GAG damage} = 0.0200$$

The average GAG damage ratio for this detail is:

$$\frac{0.0200}{0.0298} = 0.67$$

The equivalent number of GAG cycles for the life requirement becomes:

$$N_{equ} = \frac{(24272)\ (1.5)}{(0.67)} = 54{,}340 \text{ cycles}$$

Using the detail design curve defined by a DFR = 12.0, f_{max} = 2.85 ksi, and R = -0.9 for the shear web detail results in a life prediction that is very large. The economic life therefore exceeds the design life by a large margin.

5. WEIGHTS

The calculated weight of the bulkhead casting is 205.2 lb. This weight results from a detailed weight calculation of the bulkhead and includes a +2.5% increment for manufacturing tolerance. The 2.5% represents half the drawing tolerance over nominal (+0.005) on web and flange thickness. Past experience with aircraft parts calculated at nominal dimensions versus actual part weight shows this approach to be satisfactory. The density value of A357 cast aluminum was assumed to be the same as for A356, which is 0.097 $lb/in.^3$.

The weight of the finished machined bulkhead including bushings is 181.1 lb. This weight results from machining the periphery to contour and machining the interfaces for the nose gear and door actuator fittings.

The finished bulkhead weight of 181.1 lb results in a 6.5-lb weight reduction when compared to the updated baseline component weight of 187.6 lb.

6. COST

The cost summary for the YC-14 station 170 cast bulkhead is shown in figure 45. These cost figures are based on the CAST bulkhead assembly, 162-00018, using the final detail design of the station 170 bulkhead casting, 162-00017, as the major part.

	No. 1 A/P cost	300 A/P cost
Raw material	$ 1,870	$ 309,000
Labor:		
Detail and assembly tools	200,018	200,018
Foundry tools	95,000	95,000
Fabrication	10,003	1,482,313
Section installation	--	247,680
Total	$306,891	$2,334,011
Cost per unit	$306,891	$ 7,780

Figure 45. Station 170 Cast Bulkhead Costs

The raw material figure covers aluminum, sand, and binder. The aluminum, for one unit only, comes to almost 2000 lb including the bulkhead and all excess material, i.e., gates, risers, flashing, etc. For the 300-unit production run, approximately 75% of each pour is remelted and brought up to specification requirements for the next pour with completely new material used after each five castings. The sand and binder are not reusable.

The item for detail and assembly tools covers the initial hard production tooling costs only. The figure shown for the No. 1 airplane would be drastically reduced if only one unit were to be made.

The foundry tool costs cover the pattern, special mold flask tooling, and chills.

Fabrication costs for the 300-unit production run include a factored cost increment for tool maintenance and refurbishment.

The section installation costs shown are the same as shown on the updated baseline component. These costs were not recalculated based on the assumption that final installation cost differences between a built-up and a cast bulkhead would be negligible.

Engineering costs are not included here, nor are they included in the updated baseline costs in section II.5.b. For a 300-unit production run, the unit cost for engineering is relatively small, having little or no effect on the cost comparison between a built-up and a cast bulkhead.

The cost comparison between the updated baseline component as noted in section II.5.b and the detail designed cast bulkhead (fig. 45) is as shown:

$$\Delta\text{Cost} = \frac{12484 - 7780}{12484} (100) = 37.7\% \text{ reduction}$$

7. EFFECT OF DEFECTS

The occurrence of discontinuities in the castings produced during the development of foundry manufacturing procedures did not result in a wide variety of discontinuity types or sizes from which to test the effects of defects. Also, few defects were found in locations having sufficient material for specimen fabrication. The most common discontinuities encountered were gas and shrink porosity, sponge and shrinkage cavities, and less dense inclusions. Crack-like discontinuities were almost completely absent.

With a given casting, some discontinuities, such as shrinkage cavities and sponge, can be anticipated in certain locations because of an association with mold design, gating, risering, chilling, and other foundry practices. However, experience in Phase II has shown that many of the common discontinuities (dross, inclusions, and gas pores) have occurred randomly. Dispersed shrinkage porosity was somewhat controlled by type and placement of chills, but the presence of this condition away from chills was unpredictable.

The capability of NDE (nondestructive evaluation) to detect "defects" is difficult to assess quantitatively. Results of both the penetrant method for surface discontinuities and radiography for those occurring internally are highly subjective in interpretation. Industry reference standards and defect dimensional limits for penetration inspection do not exist. Reference radiographs under ASTM E155 are only comparative standards and no means of quantifying many of the defect conditions seems presently feasible. Therefore, in reality, inspectors exercise considerable individual judgement in evaluating those discontinuities that are tolerable in some approximate degree.

NDE capabilities are also significantly influenced by many manufacturing process and inspection technique variables. While it was shown that penetrant methods will reveal pore openings of the order of 0.001-inch diameter in cast surfaces, sawing, grinding, and abrasive blasting will prevent detection of these and much larger openings. Larger shallow defects also may be overlooked if technique is not closely controlled. Radiographic technique is often governed by configuration of the casting. Individual pores of 0.002-0.003 inch may be detected in 0.125-inch-thick material, but must be of the order of 0.015-inch diameter to be resolved through 0.75-inch-thick material. Also, crack-like defects must be oriented closely parallel to the incident X-ray beam to be detected in any thickness.

Because of the importance of human, processing, and technique factors, precise quantitative determination of NDE capabilities must be based on a statistical approach. Such a study is outside of the scope of this program. However, determination of what types and levels of discontinuities are truly "defects" is of initial importance. Considerable information is expected from the allowables and effects of defects data, in conjunction with fractographic examination and correlation with NDE results. When complete, this will provide some measure of actually achieved NDE capabilities, and aid in determining necessary NDE improvements and final requirements.

Improvement in NDE is needed in the following areas:

1. Assuring soundness of heavy sections, greater than 0.75-inch thickness.
2. Penetrant standards for porosity-type discontinuities.

The analytical approach to the effects of defects consists of accounting for defects in crack growth and fatigue analysis by using the equivalent initial flaws and detail fatigue ratings (DFR) for the various types of defects and X-ray grades.

The equivalent flaws and DFR's are being derived from constant-amplitude fatigue specimen tests. Specimens have been saw cut from existing castings considering the defect types and X-ray grades as presented in table 10. The specimens were located on the existing castings (20- x 40-inch fracture toughness panels and Hitchcock #9 casting) such that the defects are placed approximately in the center of the test section.

In order to evaluate specimen size effect, a number of 6- x 12-inch specimens in addition to the regular S-N specimens will be tested. The experiments will yield cycles to failure, from which equivalent initial flaws will be derived by calculating the initial dimensions of an assumed flaw that results in a crack growth life equal to the test life. DFR's will be determined from the cycles to failure according to the procedure described in appendix E of reference 2.

TABLE 10. EQUIVALENT INITIAL FLAW SIZES FOR TYPES OF DEFECTS AND X-RAY GRADES

DEFECT TYPE	X-RAY GRADES		
	B	C	D
GAS HOLES GAS POROSITY (ROUND) GAS POROSITY (ELONGATED) SHRINKAGE CAVITY SHIRNKAGE POROSITY FOREIGN MATERIAL	Equivalent Initial Flaw Sizes to be Determined from Experiments		

REFERENCES

1. "General Material Property Data," CAST Quarterly Report: April-June 1977.
2. "Damage Tolerance and Durability Control Plan," January 1977.
3. "Fracture and Fatigue Crack Growth Behavior of Surface Flaws and Flaws Originating at Fastener Holes," AFFDL Report: AFFDL-TR-74-47, May 1974.
4. Shah, R. C. and Kobayashi, A. S., "On the Surface Flaw Problem," ASME, 1972.
5. "Structural Test Plan -- Full-Scale Test," June 1977.
6. "Final Report, Phase I, Cast Aluminum Structures Technology (CAST)," AFFDL Report AFFDL-TR-77-36, May 1977.
7. "General Material Property Data," CAST Quarterly Report: July-September 1977.

APPENDIX A

LOAD ATTACHMENT POINT A ANALYSIS STRESS SPECTRUM

FLIGHT TYPE = FLIGHT TYPE NO. 1

FLIGHT TYPE = FLIGHT TYPE 1
NUMBER OF FLIGHTS IN THE BLOCK = 1
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES: UNRETAR 4.16
RETAR 4.13
DURABILITY 5.32

NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 61

LABEL	FMAX	FMIN	CYCLES	RET.FAC.	PERCENT OF LA PER FLIGHT UNRETARDED	PERCENT OF LA PER FLIGHT RETARDED	PERCENT DURABILITY
T1	.98	.89	3.00E+02	.000	.00	.00	.00
T2	1.08	.80	1.65E+02	.000	.00	.00	.00
T3	1.17	.70	2.70E+01	.000	.00	.00	.00
T4	1.26	.60	2.00E+00	.000	.00	.00	.00
T5	1.36	.52	9.00E-02	.000	.00	.00	.00
T6	1.45	.42	6.00E-03	.000	.00	.00	.00
L11	1.67	.00	3.12E+01	.000	.01	.00	.00
L12	2.24	.00	3.12E+01	.000	.02	.00	.00
L13	5.72	.00	7.40E-02	.034	.07	.02	.00
L21	3.84	.00	7.40E-02	.000	.07	.00	.00
L22	1.87	.00	1.74E+01	.000	.01	.00	.00
L23	2.53	.00	1.74E+01	.000	.02	.00	.00
L31	8.43	.00	4.30E-02	.134	.05	.07	.00
L32	4.32	.00	4.30E-02	.000	.07	.00	.00
L33	2.50	.00	1.03E+01	.000	.01	.00	.00
L51	3.36	.00	1.03E+01	.000	.05	1.04	.00
L52	6.58	.00	2.60E-02	.653	1.04	.01	.00
L53	5.76	.00	2.60E-02	.037	.16	.02	.00
L61	3.12	.00	5.20E+02	.000	.07	1.70	.00
L62	4.21	.00	5.20E+02	.000	.07	1.70	.00
L63	10.72	.00	1.30E+02	.326	1.49	.23	.00
L71	7.20	.00	1.30E+02	.000	.01	.00	.00
L72	3.75	.00	1.80E-02	.002	.08	1.08	.00
L73	5.03	.00	1.80E-02	1.000	1.08	.17	.00
L81	12.87	.00	4.00E+03	.884	.17	.01	.00
L82	6.57	.00	4.00E+03	.000	.01	.00	.00
L83	3.89	.00	8.00E+03	.052	.08	.56	.00
L91	15.00	.00	1.00E+03	1.000	.56	.10	.00
L92	10.00	.00	1.00E+03	1.000	.10	.01	.00
L93	5.72	.00	2.00E+03	.001	.01	.00	.00
L101	3.52	.00	1.00E+03	.196	.01	.01	.00
L102	7.80	.00	1.00E+03	.024	.02	.00	.00
B1	1.76	.94	5.00E+06	.468	.90	.01	.00
B2	2.27	.94	1.00E+06	.000	4.57	.00	.00
B11	2.78	.94	2.00E+06	.000	.42	.00	.00
B21	3.30	.94	1.00E+06	.000	1.67	.00	.00
T81	7.03	.94	1.07E+06	1.000	31.36	55.99	9.56
CAC	8.49	.00	1.00E+00	1.000	9.56	9.57	34.80
			1.00E+06	1.000	47.71	34.80	49.38

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

FFFF

FFFF

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

```
/*****************************  FLIGHT TYPE NO.  6  *****************************/

FLIGHT TYPE 6 FLIGHT TYPE 6
NUMBER OF FLIGHTS IN THE BLOCK = 5
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES: UNRET.=     10.72
                                            RET.=       0.00
                                    DURABILITY=        15.95
NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 41

  LABEL      FMAX      FMIN      CYCLES     RET.FAC.    PERCENT OF DA PER FLIGHT   PERCENT
                                                       UNRETARDED   RETARDED    DURABILITY
    T1        .82       .70    3.000E+02     .000          .00          .00          .00
    T2        .90       .66    1.050E+02     .000          .00          .00          .00
    T3        .98       .59    2.700E+01     .000          .00          .00          .00
    T4       1.05       .51    2.000E+02     .000          .00          .00          .00
    T5       1.13       .43    4.000E+03     .000          .00          .00          .00
    T6       1.21       .35    9.200E+01     .000          .00          .00          .00
   L11       1.29       .00    1.580E+01     .000          .00          .00          .00
   L19       1.37       .00    1.580E+01     .000          .00          .00          .00
   L21       1.45       .00    3.400E+01     .000          .00          .00          .00
   L29       2.53       .00    3.400E+02     .100          .00          .00          .00
   L31       4.32       .00    2.000E+01     .100          .00          .00          .00
   L39       2.36       .00    2.000E+01     .100          .00          .00          .00
   L41       3.58       .00    5.200E+02     .853          .00          .00          .00
   L49       5.72       .00    5.200E+02     .637          .00          .00          .00
   L51       3.11       .00    1.040E+01     .100          .00          .00          .00
   L59       4.21       .00    1.040E+02     .100          .00          .00          .00
   L61      10.72       .00    2.600E+02    1.000          .00          .00          .00
   L69       7.20       .00    2.600E+02     .426          .00          .00          .00
   L71       3.75       .00    3.600E+02     .000          .00          .00          .00
   L79       5.03       .00    3.600E+02     .102          .00          .00          .00
   L81      12.87       .00    8.000E+03    1.000          .00          .00          .00
   L89       8.65       .00    8.000E+03     .884          .00          .00          .00
   L91       4.37       .00    1.120E+02     .000          .00          .00          .00
   L99       5.89       .00    1.120E+02     .552          .00          .00          .00
   L03      15.00       .00    2.000E+03    1.000          .00          .00          .00
   L73      10.00       .00    2.000E+03    1.000          .00          .00          .00
   L77       5.00       .00    3.000E+03     .196          .00          .00          .00
   L81       5.42       .00    2.000E+03     .624          .00          .00          .00
   L83       7.57       .00    2.000E+03     .448          .00          .00          .00
   L85       1.54       .78    5.000E+00    1.000          .00          .00          .00
   A1        1.41       .78    2.000E+00    1.000          .00          .00          .00
  AL1        1.98       .00    1.000E+00    1.000          .00          .00          .00
   A2        2.42       .78    1.000E+00    1.000          .00          .00          .00
   FL1       2.86       .78    1.000E+00    1.000          .00          .00          .00
   FH1       3.42       .00    1.000E+00    1.000          .00          .00          .00
   G46       3.42       .00    1.000E+00    1.000          .00          .00          .00
```

```
FLIGHT TYPE = FLIGHT TYPE 5
NUMBER OF FLIGHTS IN THE BLOCK = 3
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSED: UNRET.=      44.15
                                            RET.=       47.60
                                     DURABILITY=        35.05
NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 65
```

LABEL		FMAX	FMIN	CYCLES	RET.FAC.	PERCENT OF DA UNRETARDED	PER FLIGHT RETARDED	PERCENT DURABILITY
T1		.82	.76	0.000E+00	.000	.00	.00	.00
T2		.90	.84	2.300E+02	.000	.00	.00	.00
T3		.20	.12	5.900E+01	.000	.00	.00	.00
T4		.23	.14	4.800E+00	.000	.00	.00	.00
T5		.25	.07	1.000E+02	.000	.00	.00	.00
T6		.26	.00	1.800E+03	.000	.00	.00	.00
111		11.87	.00	1.800E+03	.000	.00	.00	.00
112		9.76	.00	1.800E+03	.000	.00	.00	.00
113		3.20	.00	8.000E+03	.000	.00	.00	.00
114		1.87	.00	8.000E+03	.000	.00	.00	.00
115		2.53	.00	9.000E+02	.000	.00	.00	.00
116		6.43	.00	2.200E+02	.134	.00	.00	.00
117		4.32	.00	2.200E+02	.000	.00	.00	.00
118		2.50	.00	1.900E+01	.000	.00	.00	.00
119		3.36	.00	5.000E+02	.851	.00	.00	.00
120		8.58	.00	5.000E+02	.037	.00	.00	.00
121		5.74	.00	2.300E+01	.000	.00	.00	.00
122		3.12	.00	2.300E+01	.000	.00	.00	.00
123		10.72	.00	5.800E+02	1.000	1.40	2.00	2.12
124		7.20	.00	5.800E+02	.326	.00	.00	.00
125		3.75	.00	2.240E+01	.000	1.40	2.00	2.12
126		9.03	.00	2.240E+01	1.000	.28	.00	.00
127		12.87	.00	5.800E+04	1.002	.05	.00	.00
128		8.65	.00	5.800E+02	1.000	.21	.02	.00
129		5.37	.00	2.110E+01	1.000	4.44	4.72	4.95
130		9.88	.00	2.110E+01	1.000	.44	.44	.46
131		13.00	.00	5.200E+02	1.000	.10	.02	.02
132		10.09	.00	1.420E+01	1.000	.41	.04	.04
133		5.92	.00	1.420E+01	.146	8.75	9.68	9.96
134		11.55	.00	3.800E+02	1.000	11.24	1.40	1.46
135		7.67	.00	9.200E+02	1.000	.13	.00	.00
136		10.30	.00	2.230E+02	1.000	.51	.04	.04
137		12.97	.00	3.800E+02	1.000	10.56	1.03	1.08
138		8.18	.00	1.400E+02	1.000	1.63	.14	.14
139		6.31	.00	1.400E+02	.734	.54	.04	.04
140		21.20	.00	1.400E+02	1.000	11.24	1.40	1.46
141		14.25	.00	1.400E+02	1.000	1.74	.14	.14
142		9.24	.00	3.100E+02	1.000	.55	.04	.04
143		6.67	.00	3.100E+02	.233	11.12	1.40	1.46
144		23.59	.00	8.100E+03	1.000	1.72	.14	.14
145		15.85	.00	8.100E+03	1.000	.48	.04	.04
146		7.58	.00	1.000E+03	1.000	10.50	1.03	1.08
147		18.83	.00	1.000E+03	.482	1.62	.14	.14
148		17.29	.00	6.000E+03	1.000	.15	.04	.04
149		8.12	.00	1.000E+03	.955	7.88	1.40	1.46
150		10.02	.00	1.000E+03	1.000	1.56	.14	.14
151		27.07	.00	2.000E+03	1.000	.35	.04	.04
152		18.73	.00	2.000E+03	1.000	9.38	1.40	1.46
153		8.02	.00	6.000E+03	1.000	.93	.14	.14
154		11.79	.00	2.000E+03	1.000	.07	.04	.04
155		9.37	.00	5.000E+00	1.000	4.70	1.40	1.46
156		12.00	1.01	1.000E+00	.561	11.11	1.03	1.08
157		3.19	.00	1.000E+00	.075	.56	.14	.14
158		3.98	.78	1.000E+00	.395	2.79	.40	.42
159		7.42	.00	1.000E+00		11.11	1.03	1.08
160		5.88				5.72	.82	.86
161		7.42						
162								
163								
164								
165								
166								
167								
168								
169								
170								
171								
172								
173								
174								
175								
176								
177								
178								
179								
180								
181								
182								
183								
184								
185								
186								
187								
188								
189								
190								
191								
192								
193								
194								
195								
196								
197								
198								
199								
200								
201								
202								
203								
204								
205								
206								
207								
208								
209								
210								
211								
212								
213								
214								
215								
216								
217								
218								
219								
220								
221								
222								
223								
224								
225								
226								
227								
228								
229								
230								
231								
232								
233								
234								
235								
236								
237								
238								
239								
240								
241								
242								
243								
244								
245								
246								
247								
248								
249								
250								
251								
252								
253								
254								
255								
256								
257								
258								
259								
260								
261								
262								
263								
264								
265								
266								
267								
268								
269								
270								
271								
272								
273								
274								
275								
276								
277								
278								
279								
280								
281								
282								
283								
284								
285								
286								
287								
288								
289								
290								
291								
292								
293								
294								
295								
296								
297								
298								
299								
300								
301								
302								
303								
304								
305								
306								
307								
308								
309								
310								
311								
312								
313								
314								
315								
316								
317								
318								
319								
320								
321								
322								
323								
324								
325								
326								
327								
328								
329								
330								
331								
332								
333								
334								
335								
336								
337								
338								
339								
340								
341								
342								
343								
344								
345								
346								
347								
348								
349								
350								
351								
352								
353								
354								
355								
356								
357								
358								
359								
360								
361								
362								
363								
364								
365								
366								
367								
368								
369								
370								
371								
372								
373								
374								
375								
376								
377								
378								
379								
380								
381								
382								
383								
384								
385								
386								
387								
388								
389								
390								
391								
392								
393								
394								
395								
396								
397								
398								
399								
400								
401								
402								
403								
404								
405								
406								
407								
408								
409								
410								
411								
412								
413								
414								
415								
416								
417								
418								
419								
420								
421								
422								
423								
424								
425								
426								
427								
428								
429								
430								
431								
432								
433								
434								
435								
436								
437								
438								
439								
440								
441								
442								
443								
444								
445								
446								
447								
448								
449								
450								
451								
452								
453								
454								
455								
456								
457								
458								
459								
460								
461								
462								
463								
464								
465								
466								
467								
468								
469								
470								
471								
472								
473								
474								
475								
476								
477								
478								
479								
480								
481								
482								
483								
484								
485								
486								
487								
488								
489								
490								
491								
492								
493								
494								
495								
496								
497								
498								
499								
500								
501								
502								
503								
504								
505								
506								
507								
508								
509								
510								
511								
512								
513								
514								
515								
516								
517								
518								
519								
520								
521								
522								
523								
524								
525								
526								
527								
528								
529								
530								
531								
532								
533								
534								
535								
536								
537								
538								
539								
540								
541								
542								
543								
544								
545								
546								
547								
548								
549								
550								
551								
552								
553								
554								
555								
556								
557								
558								
559								
560								
561								
562								
563								
564								
565								
566								
567								
568								
569								
570								
571								
572								
573								
574								
575								
576								
577								
578								
579								
580								
581								
582								
583								
584								
585								
586								
587								
588								
589								
590								
591								
592								
593								
594								
595								
596								
597								
598								
599								
600								
601								
602								
603								
604								
605								
606								
607								
608								
609								
610								
611								
612								
613								
614								
615								
616								
617								
618								
619								
620								
621								
622								
623								
624								
625								
626								
627								
628								
629								
630								
631								
632								
633								
634								
635								
636								
637								
638								
639								
640								
641								
642								
643								
644								
645								
646								
647								
648								
649								
650								
651								
652								
653								
654								
655								
656								
657								
658								
659								
660								
661								
662								
663								
664								
665								
666								
667								
668								
669								
670								
671								
672								
673								
674								
675								
676								
677								
678								
679								
680								
681								
682								
683								
684								
685								
686								
687								
688								
689								
690								
691								
692								
693								
694								
695								
696								
697								
698								
699								
700								
701								
702								
703								
704								
705								
706								
707								
708								
709								
710								
711								
712								
713								
714								
715								
716								
717								
718								
719								
720								
721								
722								
723								
724								
725								
726								
727								
728								
729								
730								
731								
732								
733								
734								
735								
736								
737								
738								
739								
740								
741								
742								
743								
744								
745								
746								
747								
748								
749								
750								
751								
752								
753								
754								
755								
756								
757								
758								
759								
760								
761								
762								
763								
764								
765								
766								
767								
768								
769								
770								
771								
772								
773								
774								
775								
776								
777								
778								
779								
780								
781								
782								
783								
784								
785								
786								
787								
788								
789								
790								
791								
792								
793								
794								
795								
796								
797								
798								
799								
800								
801								
802								
803								
804								
805								
806								
807								
808								
809								
810								
811								
812								
813								
814								
815								
816								
817								
818								
819								
820								
821								
822								
823								
824								
825								
826								
827								
828								
829								
830								
831								
832								
833								
834								
835								
836								
837								
838								
839								
840								
841								
842								
843								
844								
845								
846								
847								
848								
849								
850								
851								
852								
853								
854								
855								
856								
857								
858								
859								
860								
861								
862								
863								
864								
865								
866								
867								
868								
869								
870								
871								
872								
873								
874								
875								
876								
877								
878								
879								
880								
881								
882								
883								
884								
885								
886								
887								
888								
889								
890								
891								
892								
893								
894								
895								
896								
897								
898								
899								
900								
901								
902								
903								
904								
905								
906								
907								
908								
909								
910								
911								
912								
913								
914								
915								
916								
917								
918								
919								
920								
921								
922								
923								
924								
925								
926								
927								
928								
929								
930								
931								
932								
933								
934								
935								
936								
937								
938								
939								
940								
941								
942								
943								
944								
945								
946								
947								
948								
949								
950								
951								
952								
953								
954								
955								
956								
957								
958								
959								
960								
961								
962								
963								
964								
965								
966								
967								
968								
969								
970								
971								
972								
973								
974								
975								
976								
977								
978								
979								
980								
981								
982								
983								
984								
985								
986								
987								
988								
989								
990								
991								
992								
993								
994								
995								
996								
997								
998								
999								
1000								

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

APPENDIX B

SHEAR WEB ANALYSIS STRESS SPECTRUM

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

FLIGHT TYPE = FLIGHT TYPE 1
NUMBER OF FLIGHTS IN THE BLOCK = 1
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES: UNRET.= 4.67
RET.= 4.00
DURABILITY= 4.00

NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 25

LABEL	PMAX	PMIN	CYCLES	RLT.FAC.	PERCENT OF UA PER FLIGHT UNRETARDED	PERCENT OF UA PER FLIGHT RETARDED	PERCENT DURABILITY
T1	.51	.48	3.000E+02	.000	.00	.00	.00
T2	.56	.41	1.650E+02	.000	.01	.00	.00
T3	.61	.36	2.700E+01	.000	.01	.00	.07
T4	.65	.31	2.000E+00	.000	.00	.00	.02
T5	.70	.27	4.000E+02	.000	.00	.00	.00
T6	.75	.22	9.000E+03	.000	.00	.00	.00
L11	1.19	-.06	3.120E+01	.104	.09	.00	.00
L12	2.12	-.10	7.400E+02	.104	.48	.05	.52
L21	1.19	-.10	1.740E+01	.000	.08	.00	.25
L22	2.12	-.14	4.300E+01	.000	.19	.00	.43
L31	1.19	-.14	1.030E+01	.000	.42	.12	.66
L32	2.12	-.18	2.400E+01	1.000	.97	1.01	.37
L41	1.19	-.18	5.200E+02	1.000	.48	.01	.71
L42	1.98	-1.24	1.300E+02	1.000	1.22	1.04	.48
L51	2.38	-1.46	1.800E+02	.283	1.01	.06	.65
L52	2.78	-1.68	4.000E+03	1.000	1.01	1.04	.25
L61	2.78	-1.74	8.000E+03	1.000	.58	.11	.25
L62	2.78	-1.80	2.000E+03	1.000	.10	.54	.25
L71	3.58	-1.90	1.000E+03	1.000	.08	.54	.13
L72	3.17	-1.98	2.000E+03	1.000	.97	.54	.13
L81	3.57	-2.23	1.000E+03	1.000	.48	.54	.13
G46	3.22	-2.23	1.000E+00	1.000	30.26	40.61	14.83
					53.00	54.83	70.44

FLIGHT TYPE = FLIGHT TYPE 2
NUMBER OF FLIGHTS IN THE BLOCK = 3
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES: UNRET.= 13.42
RET.= 10.00
DURABILITY= 10.07

NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 25

LABEL	PMAX	PMIN	CYCLES	RLT.FAC.	PERCENT OF UA PER FLIGHT UNRETARDED	PERCENT OF UA PER FLIGHT RETARDED	PERCENT DURABILITY
T1	.51	.48	3.000E+02	.000	.00	.00	.00
T2	.56	.41	1.650E+02	.000	.01	.00	.00
T3	.61	.36	2.700E+01	.000	.01	.00	.07
T4	.65	.31	2.000E+00	.000	.00	.00	.02
T5	.70	.27	4.000E+02	.000	.00	.00	.00
T6	.75	.22	9.000E+03	.000	.00	.00	.00
L11	1.19	-.06	3.120E+01	.104	.09	.00	.00
L12	2.12	-.10	7.400E+02	.104	.48	.05	.52
L21	1.19	-.10	1.740E+01	.000	.08	.00	.25
L22	2.12	-.14	4.300E+01	.000	.19	.00	.43
L31	1.19	-.14	1.030E+01	.000	.42	.12	.66
L32	2.12	-.18	2.400E+01	1.000	.97	1.01	.37
L41	1.19	-.18	5.200E+02	1.000	.48	.01	.71
L42	1.98	-1.24	1.300E+02	1.000	1.22	1.04	.48
L51	2.38	-1.46	1.800E+02	.283	1.01	1.04	.65
L52	2.78	-1.68	4.000E+03	1.000	.58	.11	.25
L61	2.78	-1.74	8.000E+03	1.000	.10	.54	.25
L62	2.78	-1.80	2.000E+03	1.000	.08	.54	.13
L71	3.58	-1.90	1.000E+03	1.000	.97	.54	.13
L72	3.17	-1.98	2.000E+03	1.000	.48	.54	.13
L81	3.57	-2.23	1.000E+03	1.000	.00	.00	.10
R1	.55	.48	5.000E+00	.000	.01	.00	.04
R2	1.17	.48	2.000E+00	.000	.00	.00	.16
RL1	1.64	.00	1.000E+00	.000	1.65	.00	1.69
TL1	3.22	.00	1.000E+00	1.000	30.26	40.61	14.83
G46	3.22	-2.23	1.000E+00	1.000	53.00	54.83	70.44

FLIGHT TYPE # FLIGHT TYPE NO. 3

FLIGHT TYPE # FLIGHT TYPE 3
NUMBER OF FLIGHTS IN THE BLOCK # 3
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES: UNIT,# 25.37
RET,# 25.31
DURABILITY# 27.32

NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE # 37

LABEL	F-MAX	F-MIN	CYCLES	RET.FAC.	PERCENT OF DA UNRETARDED	PER FLIGHT RETARDED	PERCENT DURABILITY
T1	+.42	-.38	8.000E+02	.000	.00	.00	.00
T2	+.46	-.34	3.300E+02	.000	.01	.00	.05
T3	+.10	-.10	5.400E+01	.000	.10	.00	.00
T4	+.18	-.08	4.000E+00	.000	.00	.00	.00
T5	+.19	-.07	1.600E+01	.000	.00	.00	.00
T6	+.30	-.06	8.000E+03	.000	.00	.00	.01
C11	+.77	-.53	1.500E+02	.000	.00	.00	.01
L12	1.77	-.00	4.000E+03	.005	.01	.00	.08
L21	1.19	-.74	4.500E+02	.000	.00	.00	.06
L22	2.39	-.00	2.100E+02	.280	.00	.02	.03
L31	1.58	-.98	1.800E+02	.000	.00	.00	.02
L32	3.19	-.00	2.500E+02	.000	.10	.00	.04
L41	1.98	-1.20	2.850E+01	.037	.38	.01	.00
L42	3.98	-.00	2.400E+01	1.000	1.23	1.23	1.98
L51	2.38	-1.48	1.120E+01	1.000	4.73	4.73	2.04
L52	4.78	-.00	2.600E+02	1.000	1.47	1.47	1.33
L61	2.78	-1.76	1.07[+01	.092	7.15	6.11	1.27
L62	5.57	-.00	2.[00E+02	1.000	1.80	2.05	.78
L71	3.17	-1.96	7.10[E+02	1.000	9.47	10.52	.93
L72	6.37	-.00	1.80[E+02	1.000	2.04	2.32	.92
L81	3.57	-2.23	9.00[E+02	1.000	9.85	11.18	.74
L82	7.17	-.00	1.10[E+04	1.000	1.93	2.19	.30
L91	3.92	-2.45	2.[00E+04	1.000	9.76	11.08	.08
L92	7.85	-.00	7.[00E+03	1.000	1.72	1.95	.05
L101	4.37	-2.75	1.50[E+02	1.000	9.26	10.44	.04
L102	8.76	-.00	4.00[E+03	1.000	1.54	1.75	.04
L111	4.76	-2.97	9.[00E+03	1.000	8.93	7.86	.03
L112	9.56	-.00	2.[00E+03	1.000	1.45	1.62	.03
L121	5.15	-3.22	5.00[E+03	1.000	5.04	5.72	.02
L122	10.30	-.00	1.00[E+03	1.000	1.10	1.25	.01
L131	5.60	-3.50	5.00[E+03	1.000	.49	.56	.00
L141	5.95	-3.72	1.60[E+03	.000	.01	.00	.00
R1	.60	-.60	5.00[E+01	.000	.42	.00	.00
R2	.00	-.00	2.00[E+00	.000	.37	.00	.00
RL1	1.57	-.00	1.00[E+00	.000	.37	.00	.00
RL2	2.04	-1.72	1.00[E+00	.364	8.80	5.88	.04
GAG	2.04	-1.72	1.00[E+00	.329	13.14	7.91	.04
							.00

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

```
**********************************  FLIGHT TYPE NO.  6  **********************************

FLIGHT TYPE 6 FLIGHT TYPE 6
NUMBER OF FLIGHTS IN THE BLOCK = 5                                    11.67
PCT. TOTAL BLOCK DAMAGE THIS FLIGHT CAUSES UNRET.=                     7.03
                                                  RET.=
                                  DURABILITY=                        10.03
NUMBER OF SPECTRUM INPUTS DESCRIBING FLIGHT TYPE = 25
```

LABEL	FMAX	FMIN	CYCLES	RET.FAC.	PERCENT OF DA UNRETARDED	PLN FLIGHT RETARDED	PERCENT DURABILITY
T1	+.42	+.38	3.000E+02	.000	.00	.00	.00
T2	+.46	+.34	1.850E+02	.000	.01	.00	.06
T3	+.50	+.30	2.700E+01	.000	.01	.00	.05
T4	+.55	+.26	2.000E+00	.000	.00	.00	.01
T5	+.59	+.22	9.000E+02	.000	.00	.00	.00
T6	+.63	+.18	4.000E+03	.000	.00	.00	.00
L11	+.68	-.55	9.240E+01	.000	.16	.00	.78
L12	1.77	+.00	1.58UE+01	.005	.72	.01	.42
L21	1.19	-.74	3.48UE+01	.000	.32	.00	1.18
L22	2.39	-.20	8.600E+02	.280	1.60	.75	.64
L31	1.59	-.98	2.08UE+01	.000	.74	.00	1.64
L32	3.19	.00	5.20UE+02	1.000	3.73	0.22	1.03
L41	1.99	-1.24	1.04JE+01	.037	1.07	.07	1.97
L42	3.98	.00	2.60UE+02	1.000	5.33	0.88	1.12
L51	2.39	-1.49	3.60UE+02	.263	.86	.38	1.24
L52	4.78	-.10	8.00UE+03	1.000	3.86	0.44	.65
L61	2.79	-1.74	1.20UE+02	.692	.60	.69	.70
L62	5.58	.00	2.00UE+03	1.000	1.99	3.32	.48
L71	3.37	-1.98	2.00UE+03	1.000	.26	.46	.27
L81	3.57	-2.23	5.00UE+03	1.000	.32	.54	.27
B1	.40	.40	2.00E+06	.000	.04	.00	.00
B2	.99	.40	4.00E+06	.000	.08	.00	.13
SL1	1.37	.00	1.00E+06	.000	.14	.00	1.11
TL1	2.06	.00	1.00E+06	.500	31.84	30.19	10.96
GAG	2.06	-2.23	1.00E+00	.500	45.07	42.07	75.21

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

*U.S.Government Printing Office: 1978 — 757-080/666