

AD-A062 554

MICHIGAN UNIV ANN ARBOR DEPT OF MECHANICAL ENGINEERING F/G 11/4
EFFECTS OF MOISTURE AND TEMPERATURE ON THE ELASTIC MODULI OF CO--ETC(U)
JUN 78 G S SPRINGER, C SHEN F33615-75-C-5165

UNCLASSIFIED

AFML-TR-78-86

NL

| OF |

AD
A062554



					END DATE FILMED 3-79 DDC									

ADA062554

AFML-TR-78-86

LEVEL III

A044038

2

EFFECTS OF MOISTURE AND TEMPERATURE ON THE ELASTIC MODULI OF COMPOSITE MATERIALS

THE UNIVERSITY OF MICHIGAN
MECHANICAL ENGINEERING DEPARTMENT
ANN ARBOR, MICHIGAN 48109

DDC
DEC 26 1978

DDC FILE COPY

AUGUST 1978

TECHNICAL REPORT AFML-TR-78-86
Interim Report for Period March 1977 - March 1978

Approved for public release; distribution unlimited.


AIR FORCE MATERIALS LABORATORY
AIR FORCE WRIGHT AERONAUTICAL LABORATORIES
AIR FORCE SYSTEMS COMMAND
WRIGHT-PATTERSON AIR FORCE BASE, OHIO 45433

78 12 20 015

NOTICE


When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

This technical report has been reviewed and is approved for publication.



S. W. TSAI, Project Engineer
Mechanics & Surface Interactions Br.
Nonmetallic Materials Division

FOR THE COMMANDER:



J. M. KELBLE, Chief
Nonmetallic Materials Division

"If your address has changed, if you wish to be removed from our mailing list, or if the addressee is no longer employed by your organization please notify AFML/MBM, W-P AFB, OH 45433 to help us maintain a current mailing list".

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

19. REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 18 AFML-TR-78-86	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) 6 Effects of Moisture and Temperature on the Elastic Moduli of Composite Materials.		5. TYPE OF REPORT & PERIOD COVERED 9 Technical-Annual <i>rept.</i> March 1977-March 1978
7. AUTHOR(s) 10 George S. Springer Chi-Hung Shen		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS The University of Michigan Department of Mechanical Engineering Ann Arbor, Michigan 48109		8. CONTRACT OR GRANT NUMBER(s) 15 F33615-75-C-5165
11. CONTROLLING OFFICE NAME AND ADDRESS Air Force Materials Laboratory (AFML/MBM) Air Force Wright Aeronautical Laboratories Wright-Patterson Air Force Base, Ohio 45433		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 16 734003A5 17 93
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE 11 June 1978
		13. NUMBER OF PAGES 45 12, 45 p.
		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Moisture Absorption and Desorption Buckling Modulus Elastic Moduli Graphite Epoxy Composites		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The buckling modulus of Thornel 300/Fiberite 1034 graphite epoxy composites was measured at temperatures ranging from 195 K to 422 K and the moisture content from 0% (dry) to 1.5% (fully saturated). The measurements were made using 0°, 90° and $\pi/4$ laminates. A survey was also made of the existing data showing the effects of temperature and moisture content on the tensile modulus and the compressive modulus of different composite materials.		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED 407 426

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

degree

pi

78 12 20 015

not

FOREWORD

This annual report was submitted by Dr. George S. Springer and Dr. Chi-Hung Shen of The University of Michigan, Mechanical Engineering Department, Ann Arbor, Michigan, under contract F33615-75-C-5165, Project 7340, Task 734003, with the Air Force Materials Laboratory, Wright-Patterson Air Force Base, Ohio. Stephen W. Tsai, AFML-MBM was the laboratory project monitor.

This report is for the project period March 1977 to March 1978. The work performed during the previous year (March 1976 to March 1977) was described in AFML TR-77-82 "Effects of Moisture and Temperature on the Tensile Strength of Composite Materials."

#044058

ACCESSION for	
DTIC	Wing Section <input checked="" type="checkbox"/>
DDI	DTIC Section <input type="checkbox"/>
UNCLASSIFIED	
NOT RELEASABLE	

TABLE OF CONTENTS

Section	Page
I INTRODUCTION	1
II CONCLUSIONS	1
III EXPERIMENTAL	3
IV RESULTS	8
REFERENCES	35

LIST OF ILLUSTRATIONS

Figure	Page
1. Graph of Compressive Load versus Cross-Head Displacement in a Typical Buckling Test. 90° Specimen at 300 K and 0% Moisture Content	5
2. Graph of Log σ_{cr} versus Log L for 90° Specimens at 300 K and 0% Moisture Content	7
3. Buckling Modulus of Thornel 300/Fiberite 1034 as a Function of Temperature and Moisture Content. Present Data	9
4. Tensile Modulus of Hercules AS-5/3501 as a Function of Temperature and Moisture Content. Data of Browning et al. 1976 [5] ...	13
5. Tensile Modulus of Hercules AS-5/3501 as a Function of Temperature and Moisture Content. Data of Verette, 1975 [6]	14
6. Dry Longitudinal and Quasi-Isotropic Tensile Moduli of Hercules AS-5/3501 as a Function of Temperature. Data of Kerr et al. 1975 [7]	15
7. Tensile Modulus of Thornel 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1975 [8]...	16
8. Transverse Tensile Modulus of Thornel 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Husman, 1976 [9]	17
9. Tensile Modulus of Modmor II/Narmco 5206 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1974 [10]	18
10. Tensile Modulus of Courtaulds HMS/Hercules 3002M as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10]	19
11. Quasi-Isotropic Tensile Modulus of HT-S/ERLA-4617 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]	20
12. Quasi-Isotropic Tensile Modulus of HT-S/Fiberite X-911 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]	21
13. Quasi-Isotropic Tensile Modulus of HT-S/UCC X-2546 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]	22
14. Dry Longitudinal Tensile Modulus of PRD-49/ERLB-4617 as a Function of Temperature. Data of Hanson, 1972 [12]	23

Figure	Page
15. Transverse Tensile Modulus of HT-S/(8183/137-NDA-BF ₃ : MEA) as a Function of Temperature and Moisture Content. Data of Hertz, 1973 [13]	24
16. Quasi-Isotropic Tensile Modulus of HT/S/Hysol ADX-516 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]	25
17. Dry Longitudinal and Quasi-Isotropic Tensile Moduli of HT-S/710 Polyimide as a Function of Temperature. Data of Kerr et al. 1975 [7]	26
18. Dry Quasi-Isotropic Tensile Modulus of HT-S/P13N Polyimide as a Function of Temperature. Data of Browning, 1972 [11]	27
19. Tensile Modulus of Boron/AVCO 5505 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1974 [10]	28
20. Quasi-Isotropic Tensile Modulus of Boron/Narmco 5505 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]. ○ △ : Post-Cured Specimen; ● ▲ : Not Post-Cured Specimen	29
21. Longitudinal and Transverse Compressive Moduli of Hercules HS-5/3501 as a Function of Temperature and Moisture Content. Data of Verette, 1975 [6]	30
22. Compressive Modulus of Thornel 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1975 [8]	31
23. Compressive Modulus of Modmor II/Narmco 5206 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1974 [10]	32
24. Compressive Modulus of Courtaulds HMS/Hercules 3002M as a Function of Temperature and Moisture Content. Data of Hofer et al. 1974 [10]	33
25. Compressive Modulus of Boron/AVCO 5505 as a Function of Temperature and Moisture Content. Data of Hofer et al. 1974 [10]	34

LIST OF TABLES

Table		Page
1	Summary of Experimental Data on the Effects of Moisture and Temperature on the Elastic Modulus of Composite Materials	10

LIST OF SYMBOLS

b	width of specimen (mm)
ϵ	experimental error defined in eq. (3) (Pa)
E_b	buckling modulus (Pa)
E_c	compressive modulus (Pa)
E_t	tensile modulus (Pa)
h	thickness of specimen (mm)
I	moment of inertia of the cross sectional area (mm^4)
L	length of specimen (mm)
N	number of buckling tests (dimensionless)
P_{cr}	critical buckling load (N)
S	sum of the squares of the errors defined in eq. (4) (Pa^2)
σ_{cr}	critical buckling stress (Pa)

I. INTRODUCTION

In order to utilize the full potential of composite materials their performance during and after exposure to high temperature and high humidity environments must be known. One of the most important parameters in the design of composite elements and structures is the elastic modulus. The effects of temperature and moisture content on tensile (E_t) and compressive (E_c) moduli have been studied in the past. The objective of this investigation was to evaluate the changes in the buckling modulus (E_b) of composite materials exposed to air in which the temperature ranged from 195 K to 450 K and the moisture content from 0% (dry) to 1.5% (fully saturated). The changes in the buckling modulus were measured by performing buckling tests on Thornel 300/Fiberite 1034 graphite epoxy composites using 0° , $\pi/4$ and 90° lay-ups. A summary was also made of the existing data. This summary, together with the present results, was used to assess the influence of the temperature and the moisture content on the elastic moduli of composite materials.

II. CONCLUSIONS

On the basis of both the present data (for buckling modulus) and the existing data (for tensile and compressive moduli, Table 1) the following general conclusions may be drawn.

(1) Temperature Effects

(a) For 0° and $\pi/4$ laminates the temperature (in the range of 200 K to 450 K) has a negligible effect on the elastic moduli regardless of the moisture content of the material.

(b) For 90° laminates an increase in temperature causes a decrease in the elastic moduli. The decrease in the modulus depends upon both the

temperature and the moisture content. For an increase in temperature from 300 K to 450 K the elastic modulus may decrease by as much as 50 to 90 percent.

(2) Moisture Effects

(a) For 0° and $\pi/4$ laminates there appears to be very little change in the elastic moduli over the entire spectrum of moisture content from dry to fully saturated. This conclusion appears to be valid regardless of temperature in the range 200 K to 450 K.

(b) For 90° laminates the elastic moduli decrease considerably with increase in the moisture content. The decrease in the modulus depends both on the moisture content and on the temperature. The decrease in the value of the modulus may be as high as 50 to 90 percent.

(c) In the tests reported here the moisture distribution was nonuniform inside the specimens. For 0° and $\pi/4$ specimens the variations encountered in the moisture distribution do not appear to affect the results significantly. For 90° specimens the moisture distribution may influence the absolute value of the buckling moduli, but is unlikely to affect the trend in the data.

(3) Additional Considerations

(a) The values of the elastic moduli obtained by tensile, compressive and buckling tests are usually different. However, the changes in the moduli caused by changes in temperature and moisture content are nearly the same for all three moduli. Therefore, the conclusions stated in points 1 and 2 above are valid for all three elastic moduli.

(b) The above conclusions depict the general trend in the data. The precise effects of the temperature and the moisture content on a particular com-

posite material must be evaluated from the relevant data. A ± 20 percent scatter in the data is quite common. This scatter must be borne in mind when applying the data.

III. EXPERIMENTAL

All buckling measurements in this study were made with 8 ply T300/1034 specimens of thickness $h = 0.9$ mm and width $b = 4.76$ mm. Different length specimens were used in the tests, the lengths ranging from 36 mm to 318 mm. The test specimens were cut from 0.66 m x 0.66 m autoclave cured panels which were fabricated from 30.5 cm (12 in) prepreg (Fiberite Corp.) using standard lay-up and vacuum bagging procedures. The cure cycle used in manufacturing the panels was described in [1].

Prior to the buckling tests all the specimens were completely dried at 366 K in a desiccator. The specimens were then placed in environmental chambers [2] in which the temperature and the relative humidity were kept constant at 366 K and 100%. The specimens were kept in the chambers until the moisture content (weight gain) reached the required level, i.e. until the specimen was fully saturated or until the moisture contents reached 1/3 or 2/3 of the fully saturated value. At 1/3 and 2/3 saturation the moisture distribution was nonuniform inside the specimen. This moisture distribution at these saturation levels was given by Shen and Springer [1].

The buckling moduli were determined using a 10,000 lb capacity Instron machine (Model TTCLM 1-4). At the start of each test the specimen was placed between two 15.3 cm diameter smooth metal discs attached to the Instron machine. The ends of the specimen were not restrained in any other way. The specimen was compressed along its length at a cross-head speed of 1.27 mm min^{-1} (0.05 in/min). The load was recorded continuously during the test. As the

specimen was compressed the load increased to a peak. The load then decreased and levelled off, remaining nearly constant with displacement, as shown in Fig. 1. The value of this constant load, designated as the critical load P_{cr} , is related to the buckling modulus by the expression [3]

$$P_{cr} = \frac{\pi^2 I E_b}{L^2} \quad (1)$$

where E_b is the buckling modulus, I is the moment of inertia of the cross sectional area ($I = bh^3/12$) and L is the length of the specimen.

By rewriting eq. (1) in terms of the critical stress σ_{cr} , we obtain

$$\sigma_{cr} = \frac{P_{cr}}{bh} = \frac{\pi^2 h^2 E_b}{12 L^2} \quad (2)$$

In order to evaluate E_b for a given environmental condition, a large number of buckling tests were performed using specimens of different lengths. For each environmental condition at least 12 buckling tests were performed using specimens of lengths 56, 89, and 172 mm. At room temperature (300 K, 0% moisture content) 25 specimens with lengths ranging between 36 mm and 318 mm were tested. The buckling modulus was then determined as follows.

The experimental error (ϵ) in the data is defined as

$$\epsilon \equiv \sigma_{cr} - \frac{\pi^2 h^2 E_b}{12 L^2} \quad (3)$$

For N number of tests, the sum of the squares of the errors S is

$$S = \sum_{i=1}^N (\epsilon_i)^2 \quad (4)$$

or

$$S = \sum_{i=1}^N \left(\sigma_{cr_i} - \frac{\pi^2 h^2 E_b}{12 L_i^2} \right)^2 \quad (5)$$

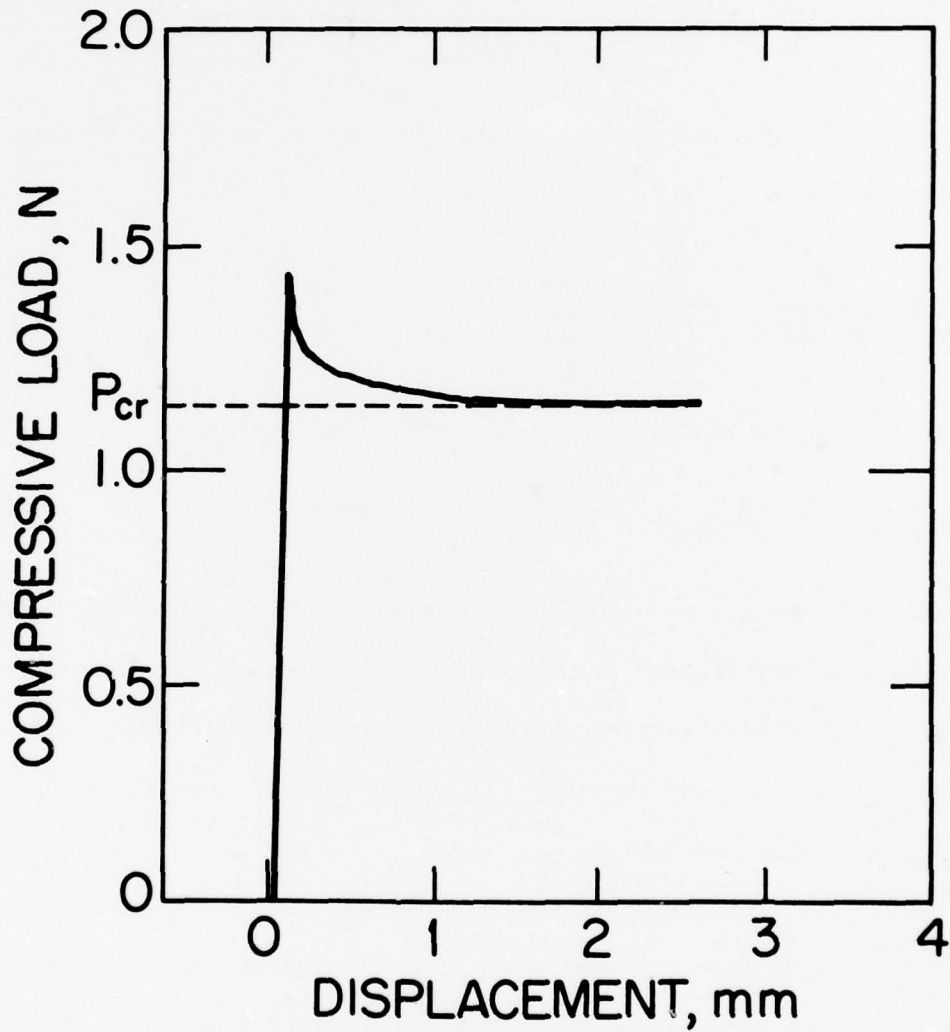


Figure 1. Graph of Compressive Load Versus Cross-Head Displacement in a Typical Buckling Test. 90° Specimen at 300 K and 0% Moisture Content.

The subscript i denotes the i th test. The value of E_b which makes S a minimum is taken as the buckling modulus. Differentiating eq. (5) with respect to E_b yields

$$\frac{dS}{dE_b} = \sum_{i=1}^N 2 \left(\zeta_{cr_i} - \frac{\pi^2 h^2 E_b}{12 L_i^2} \right) \left(- \frac{\pi^2 h^2}{12 L_i^2} \right) \quad (6)$$

By equating eq. (6) to zero and solving for the value of E_b , we obtain the required value of E_b

$$E_b = \frac{12}{\pi^2 h^2} \frac{\sum_{i=1}^N \frac{\zeta_{cr_i}}{L_i^2}}{\sum_{i=1}^N \frac{1}{L_i^2}} \quad (7)$$

It is noted that eq. (2) may be written in the form

$$\log \zeta_{cr} = \log \frac{\pi^2 h^2 E_b}{12} - 2 \log L \quad (8)$$

According to this equation, on a $\log \zeta_{cr}$ versus $\log L$ plot, the data should fall on a straight line of slope-2. In order to check the accuracy of the present data, all the data were plotted on such a graph. For all test conditions the data followed closely a straight line of slope-2. A typical set of results is shown in Fig. 2.

During each buckling test the specimen was maintained at the desired temperature by an infrared heat lamp. The temperature of the specimen was measured by a copper-constantan thermocouple attached to the surface of the specimen. The moisture content of the environment was not controlled during the buckling test, and hence some drying of the outer layer of the specimen might have occurred during the test. The thickness of the layer affected by the drying and the amount of moisture lost during this drying was calculated, and was reported in ref. [1].

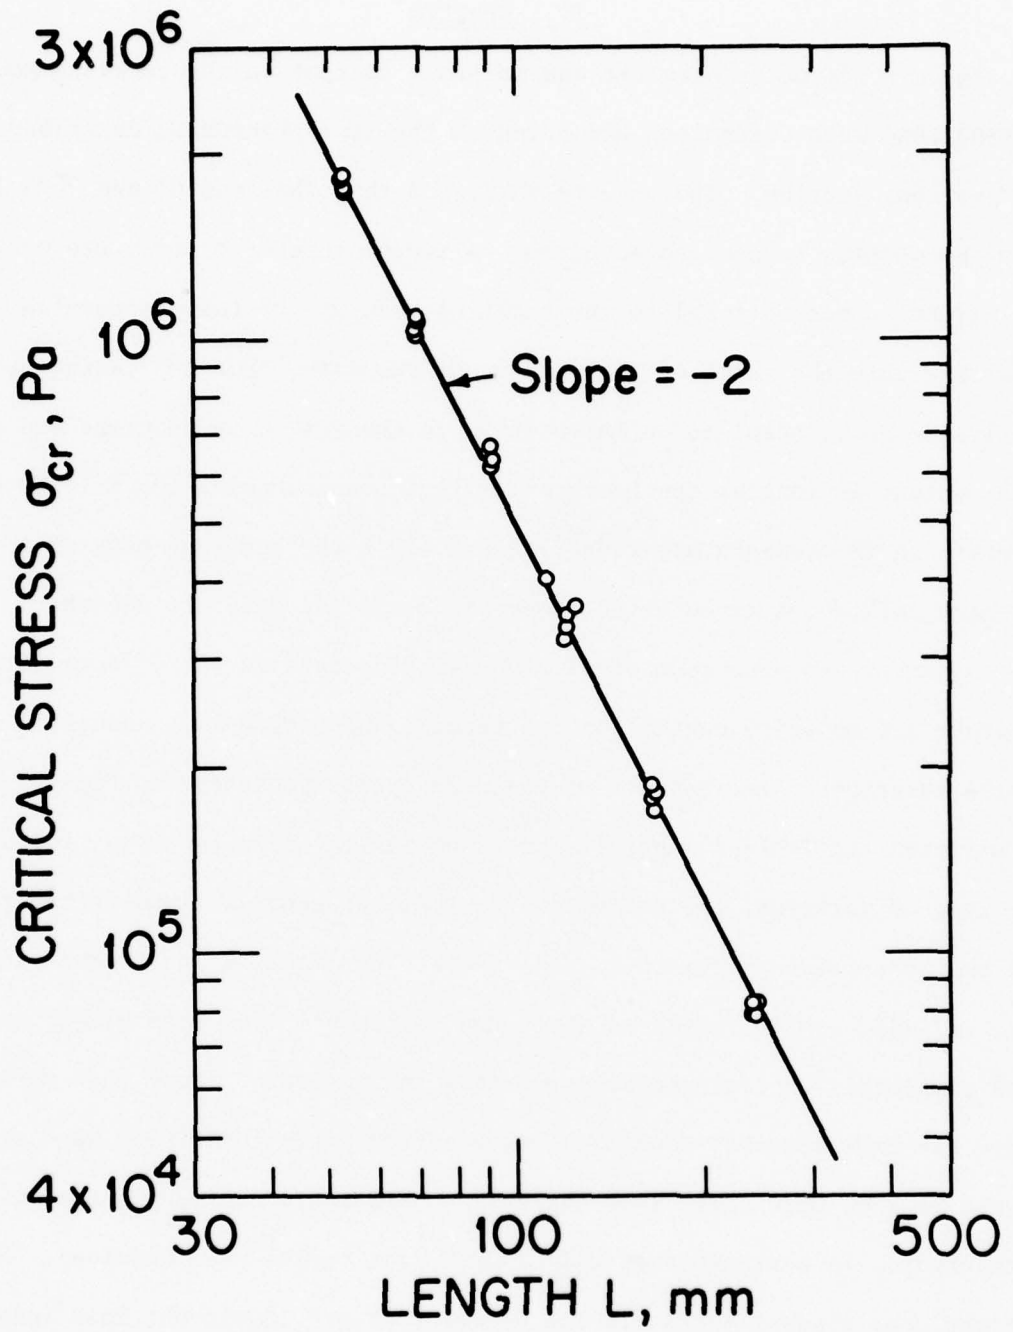


Figure 2. Graph of $\log \sigma_{cr}$ Versus $\log L$ for 90° Specimens at 300 K and 0% Moisture Content.

IV. RESULTS*

The effects of temperature and moisture content on the buckling modulus of T300/1034 were determined according to the test procedures described in the previous section. The results in Fig. 3 show that for 0° and $\pi/4$ laminates the modulus is unaffected either by temperature or by moisture content. The slight decrease ($\sim 5\%$) in the buckling modulus for fully saturated specimens is within the range of the scatter of the data. For 90° laminates the buckling modulus seems to be insensitive to changes in temperature and moisture content as long as the temperature is in the range of 195 K - 300 K. However, in the temperature range 300 K - 450 K the buckling modulus is strongly influenced by both the temperature and the moisture content.

A survey was also made of all the existing data on the effects of temperature and moisture content on the tensile and compressive moduli of composite materials. The results of this survey are presented in Figs. 4-25. In addition, in Table 1 a brief summary of all the data is given, including the type of material, the parameters varied, the general trend in the results, and the appropriate references. All those experiments known to the authors were included in the survey in which the test conditions were either specified completely or could be assessed from the reports. Those test results where the environmental conditions were not properly identified were excluded. As can be seen from Figs. 4-25 there is considerable scatter in the data. Furthermore, in certain cases only 2 or 3 data points were obtained. Nevertheless, the general trends in the behavior of previously obtained tensile and compressive moduli (Figs. 4-25) are similar to the behavior of the buckling moduli obtained in the present study (Fig. 3).

* Note: $1 \text{ GPa} = 1.45 \times 10^5 \text{ lbf/in}^2$

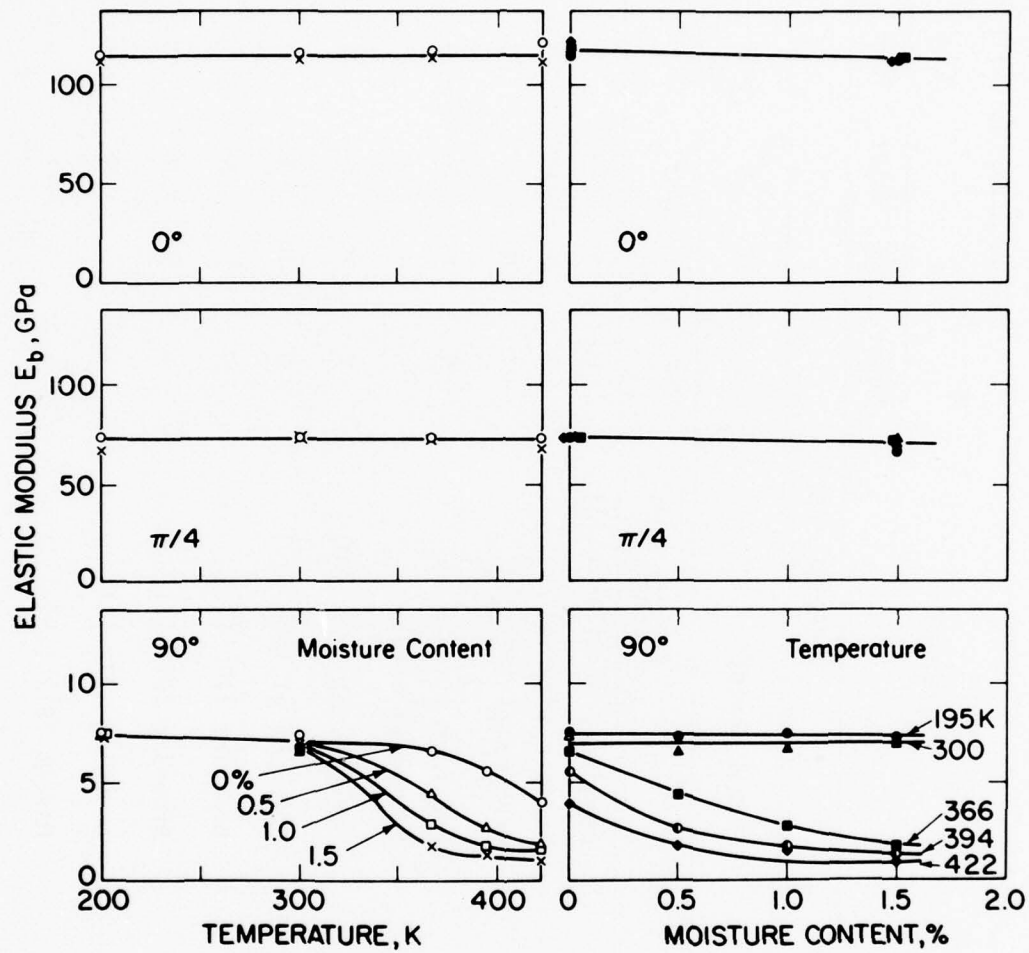


Figure 3. Buckling Modulus of Thornel 300/Fiberite 1034 as a Function of Temperature and Moisture Content. Present Data.

Table 1. Summary of Experimental Data on the Effects of Moisture and Temperature on the Elastic Modulus of Composite Materials

Composite	Reference	Laminate Lay-Up Orientation					
		0°		$\pi/4$		90°	
		Moist	Temp	Moist	Temp	Moist	Temp
BUCKLING TEST							
Thornel 300/Fiberite 1034	Shen & Springer 1977	N	N	N	N	S	S
TENSILE TEST							
Hercules AS-5/3501	Browning, et al 1976 [5]	L	N	L	N	S	S
	Verette 1975 [6]	N	N	N	-	S	S
	Kerr, et al 1975 [7]	-	N	-	N	-	-
Thornel 300/Narmco 5208	Hofer, et al 1975 [8]	N	N	N	N	N	N
	Husman 1976 [9]	-	-	-	-	S	S
Modmor II/Narmco 5206	Hofer, et al 1974 [10]	N	N	N	N	S	S
Courtaulds HMS/Hercules 3002M	Hofer, et al 1974 [10]	N	N	N	N	N	S
HT-S/ERLA-4617	Browning 1972 [11]	-	-	N	S	-	-
HT-S/Fiberite X-911	Browning 1972 [11]	-	-	N	N	-	-
HT-S/UCC X-2546	Browning 1972 [11]	-	-	N	L	-	-
PRD-49/ERLB-4617	Hanson 1972 [12]	-	S	-	-	-	-
HT-S/(8183/137-NDA-BF ₃ : MEA)	Hertz 1973 [13]	-	-	-	-	N	S

Table 1. (continued)

Composite	Reference	Laminate Lay-Up Orientation					
		0°		$\pi/4$		90°	
		Moist	Temp	Moist	Temp	Moist	Temp
TENSILE TEST							
HT-S/Hyso1 ADX-516	Browning 1972 [11]	-	-	N	S	-	-
HT-S/710 Polyimide	Kerr, et al 1975 [7]	-	N	-	N	-	-
HT-S/P13N Polyimide	Browning 1972 [11]	-	-	-	L	-	-
Boron/AVCO 5505	Hofer, et al 1974 [10]	N	N	N	N	S	S
Boron/Narmco 5505	Browning 1972 [11]	-	-	N	N	-	-
COMPRESSIVE TEST							
Hercules AS-5/3501	Verette 1975 [6]	N	N	-	-	L	S
Thorne1 500/Narmco 5208	Hofer, et al 1975 [8]	L	N	N	N	L	N
Modmor II/Normco 5206	Hofer, et al 1974 [10]	N	N	N	N	S	S
Courtaulds HMS/Hercules 3002M	Hofer, et al 1974 [10]	N	N	N	N	S	S
Boron/AVCO 5505	Hofer, et al 1974 [10]	N	N	N	N	S	S

a) N = Negligible effect

b) L = Little effect (<30%)

c) S = Strong effect (>30%)

Figures 3-25 may be used to evaluate the effects of temperature and moisture content on the tensile, compressive and buckling moduli of different composites. Figures 3-25 also indicate the conditions where data are lacking.

It is finally noted that the effects of temperature and moisture content on the three moduli (E_t , E_c , E_b) are very similar to those on the ultimate tensile strength [1].

It is emphasized again that the results presented illustrate the trend in the buckling moduli. In addition to temperature and humidity, other parameters such as cure cycle, temperature history (thermal spikes), and loading history may influence the absolute value of the buckling modulus.

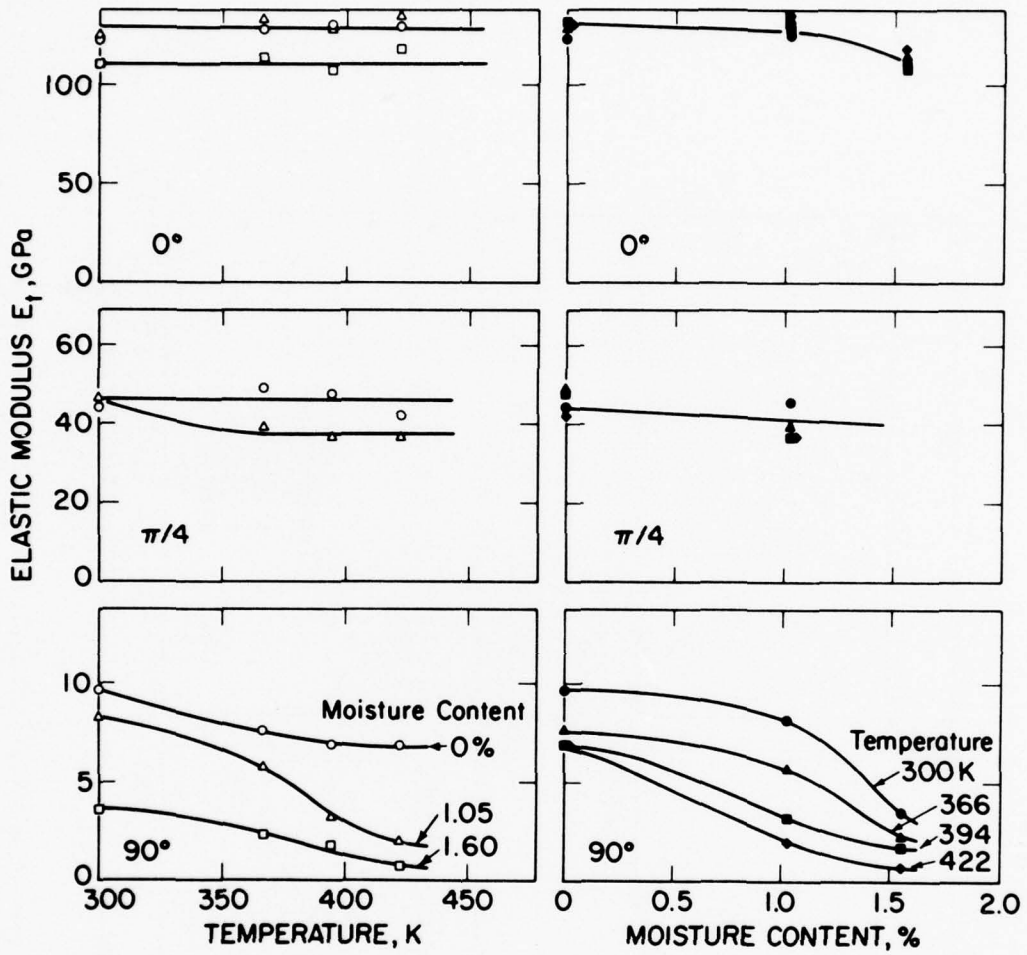


Figure 4. Tensile Modulus of Hercules AS-5/3501 as a Function of Temperature and Moisture Content. Data of Browning, et al. 1976 [5].

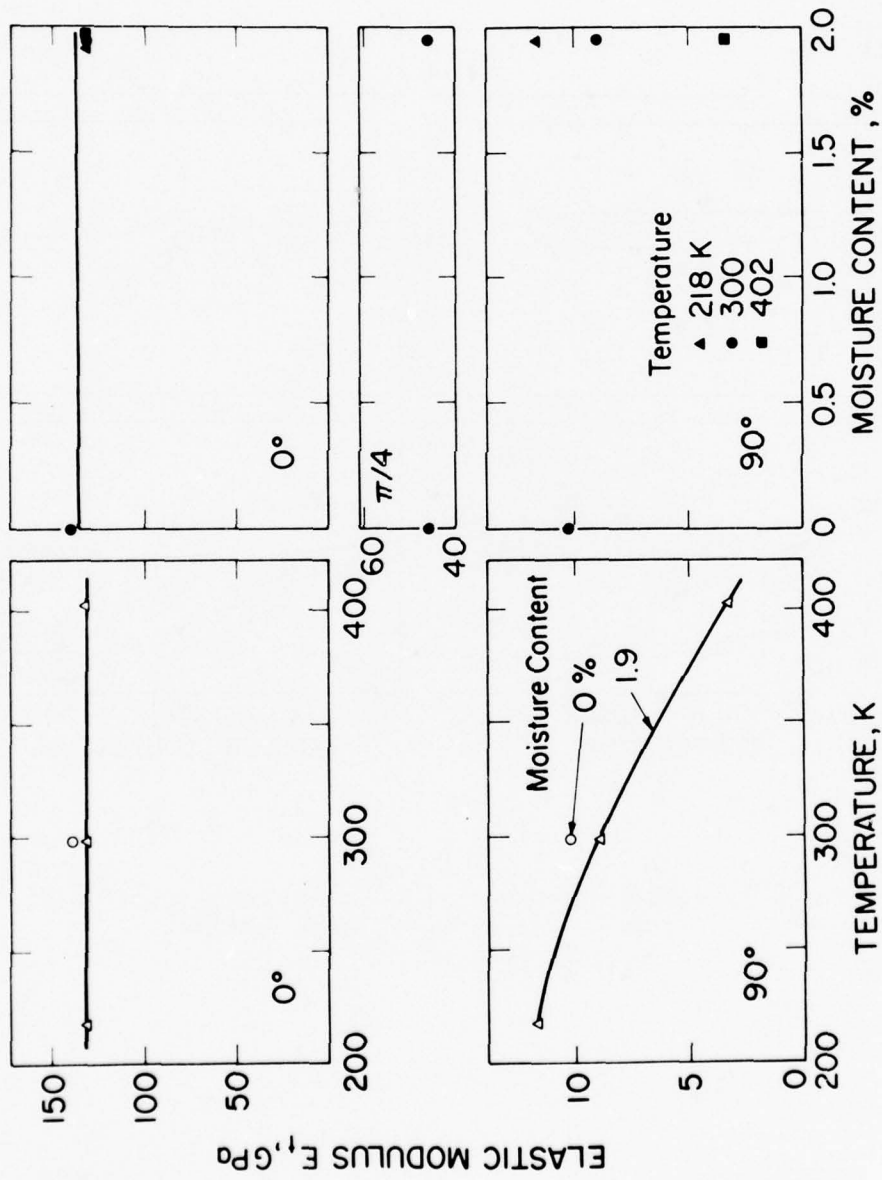


Figure 5. Tensile Modulus of Hercules AS-5/3501 as a Function of Temperature and Moisture Content. Data of Verette, 1975 [6].

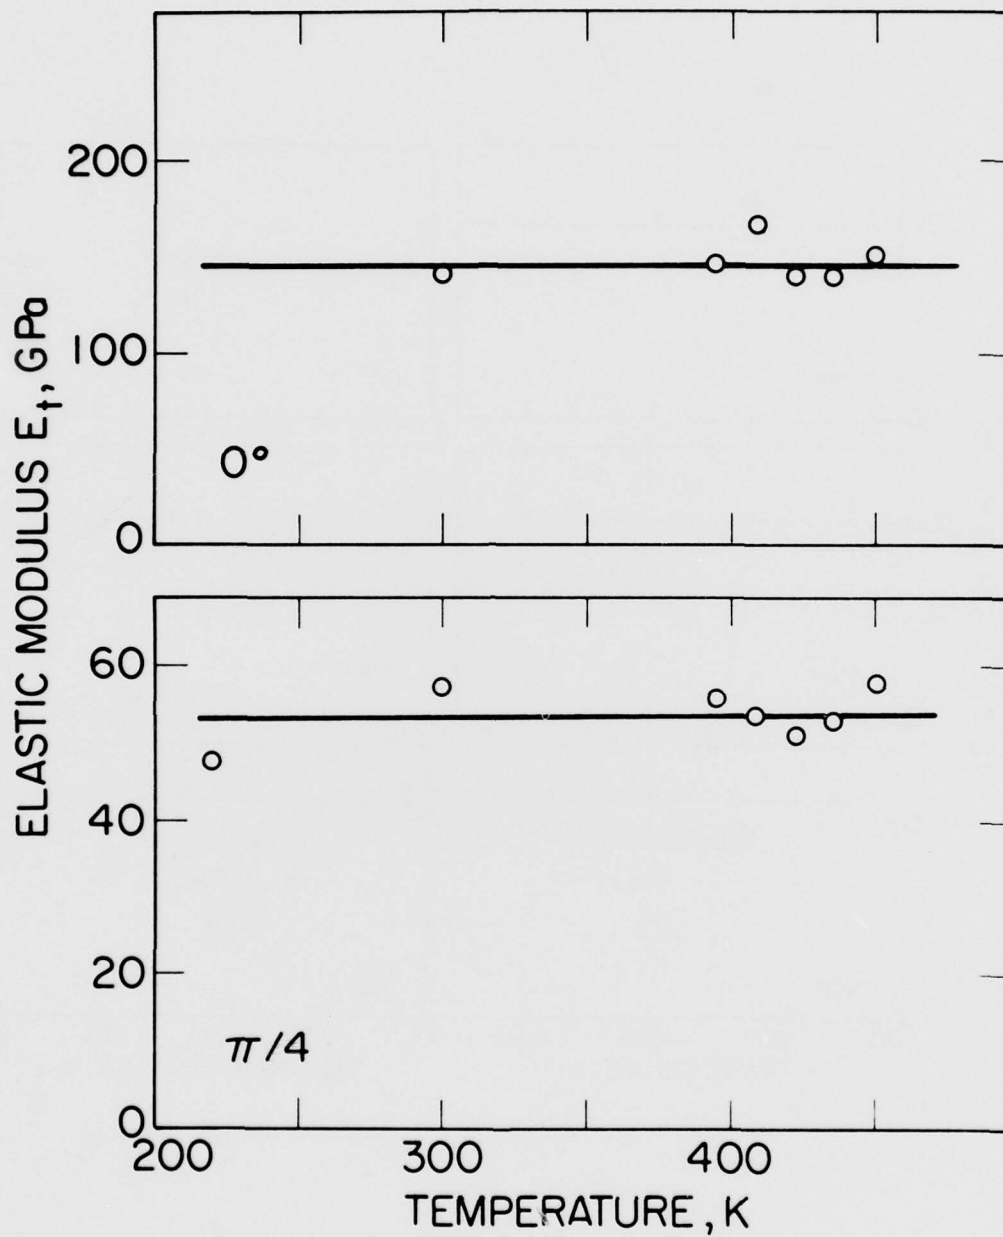


Figure 6. Dry Longitudinal and Quasi-Isotropic Tensile Moduli of Hercules AS-5/3501 as a Function of Temperature. Data of Kerr et al. 1975 [7].

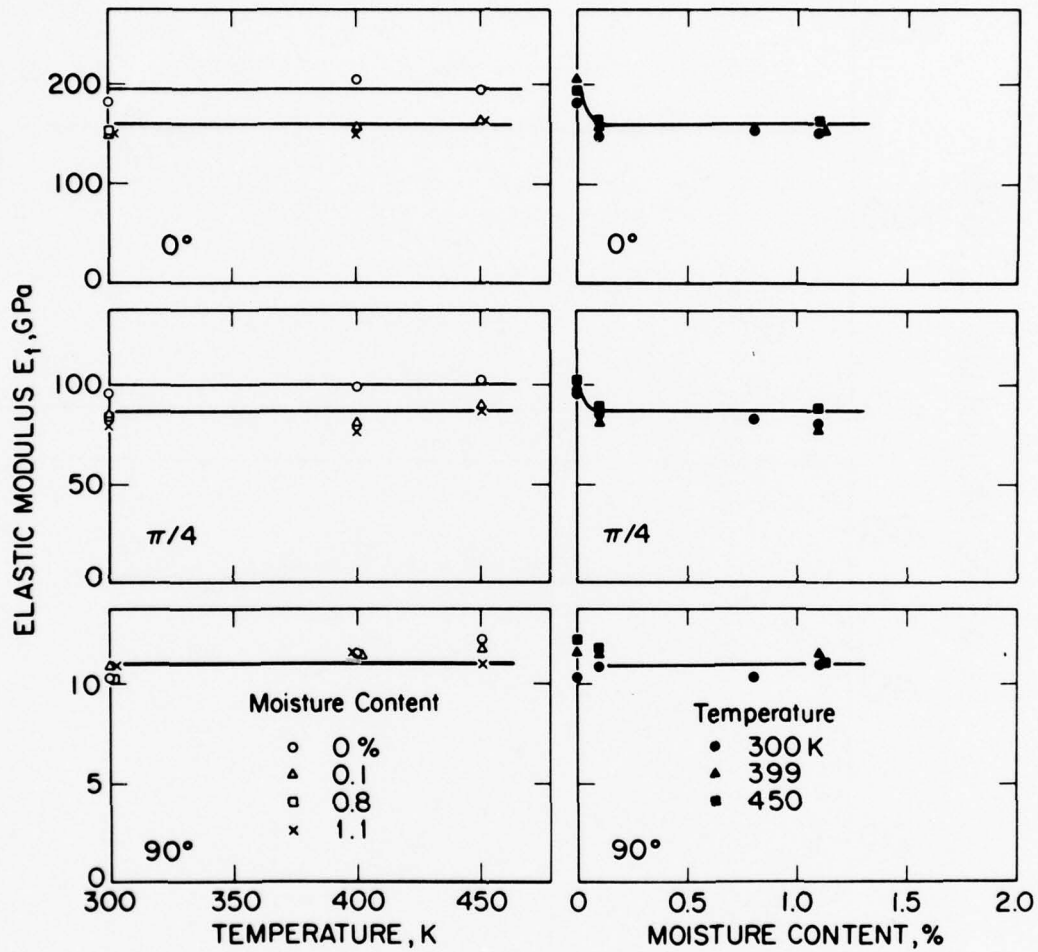


Figure 7. Tensile Modulus of Thorne1 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1975 [8].

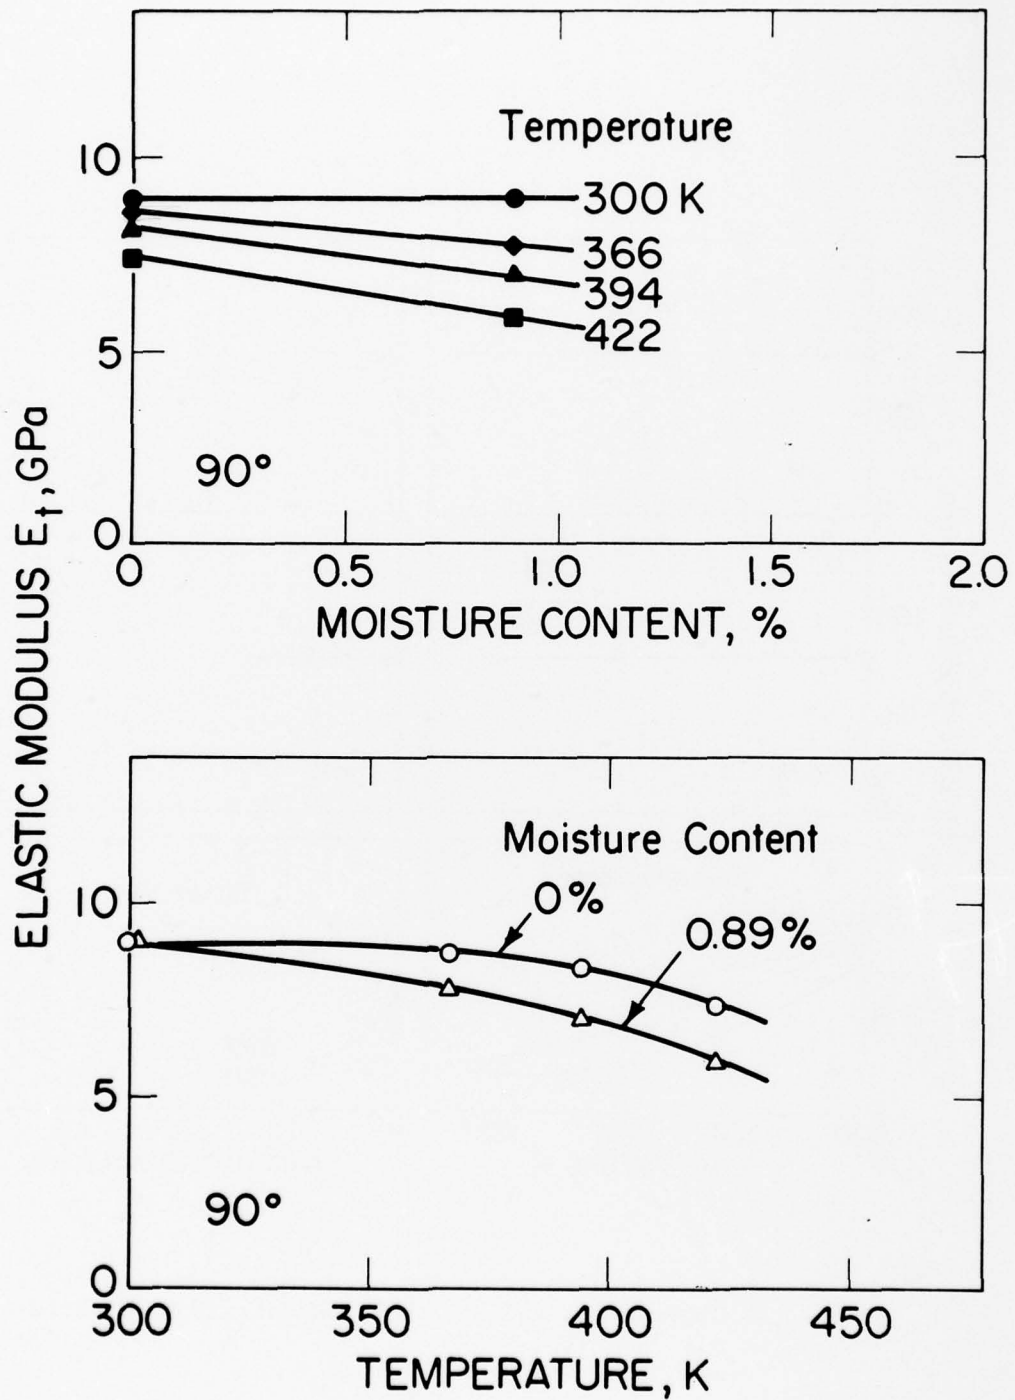


Figure 8. Transverse Tensile Modulus of Thorne1 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Husman, 1976 [9].

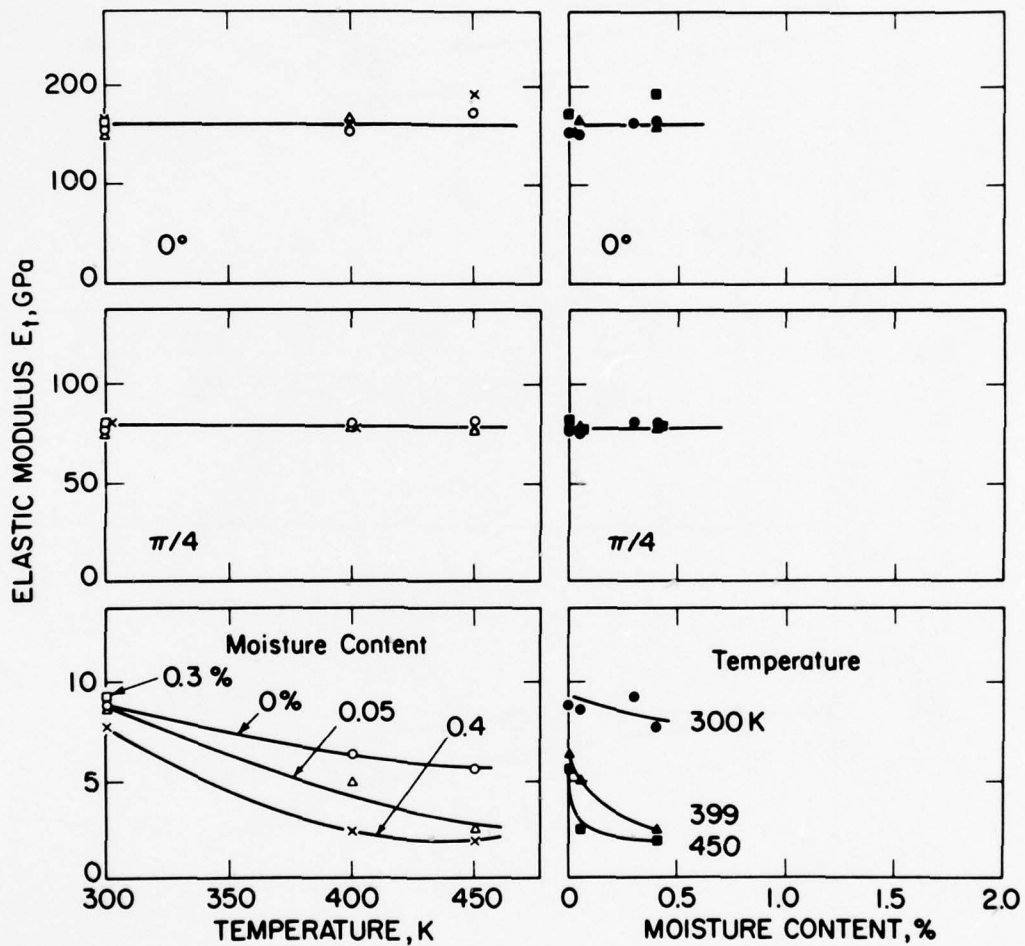


Figure 9. Tensile Modulus of Modmor II/Narmco 5206 as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10].

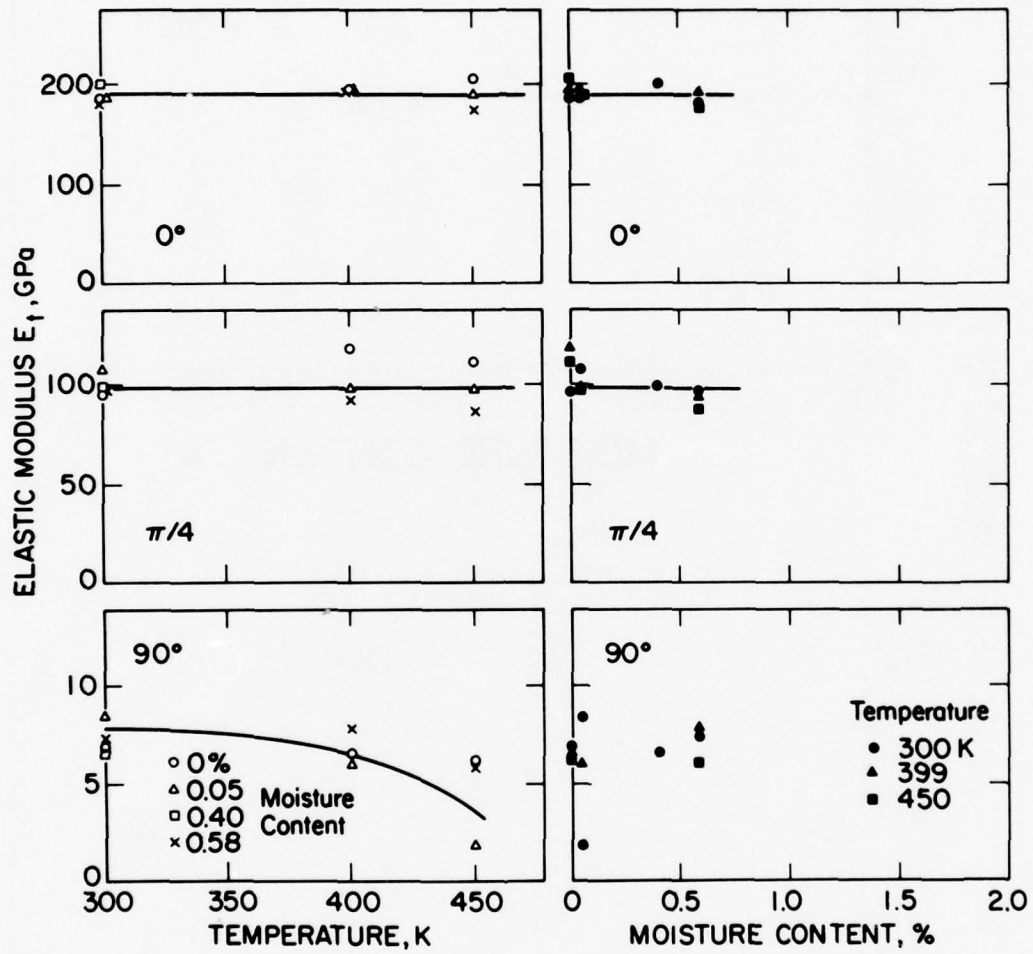


Figure 10. Tensile Modulus of Courtaulds HMS/Hercules 3002M as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10].

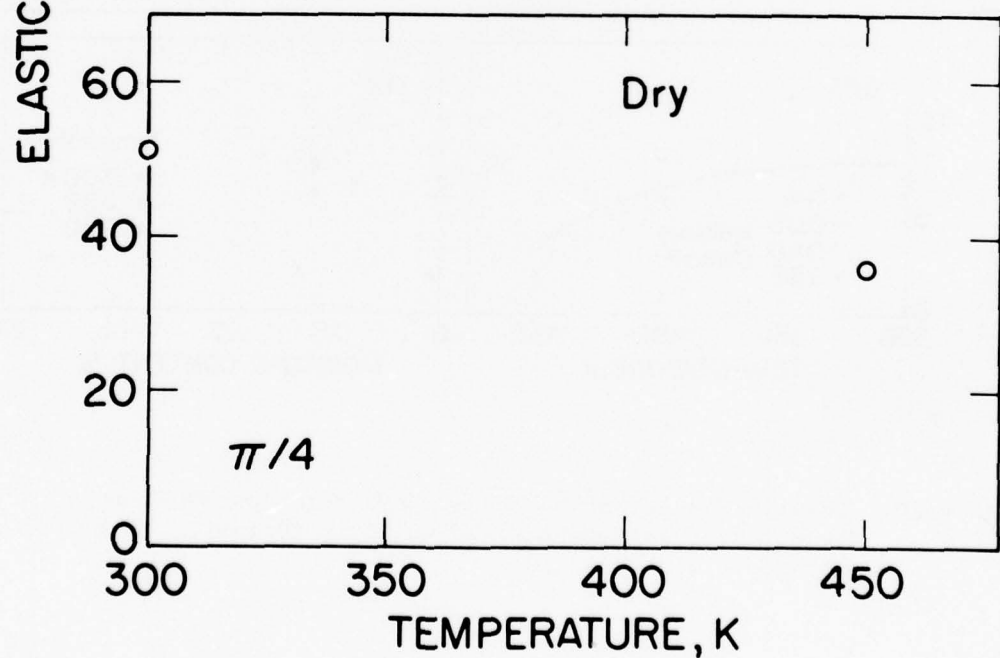
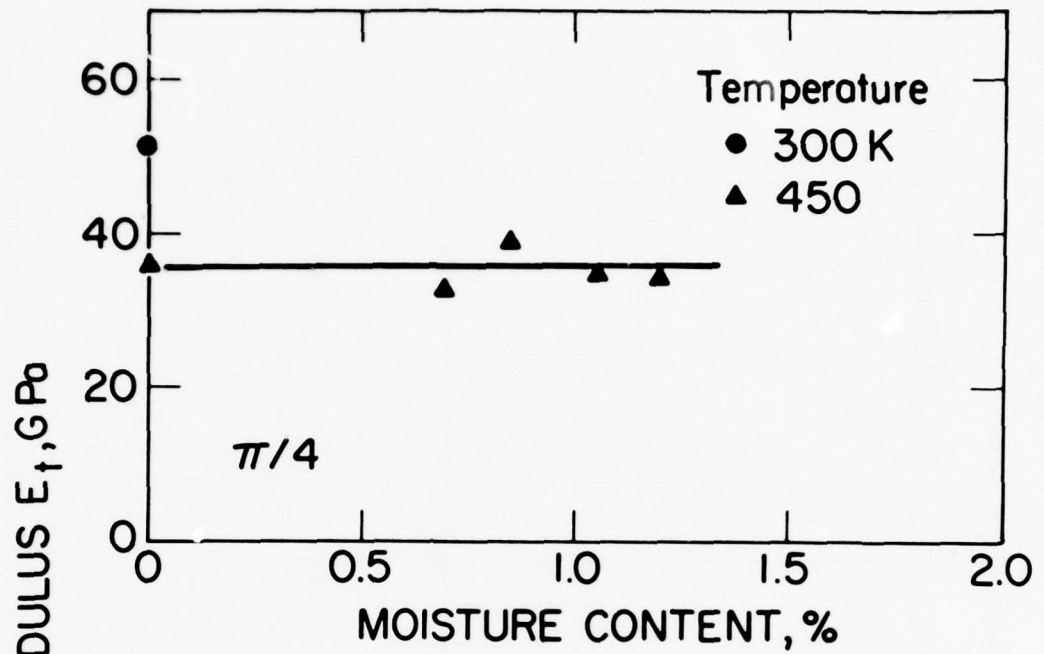


Figure 11. Quasi-Isotropic tensile modulus of HT-S/ERLA-4617 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11].

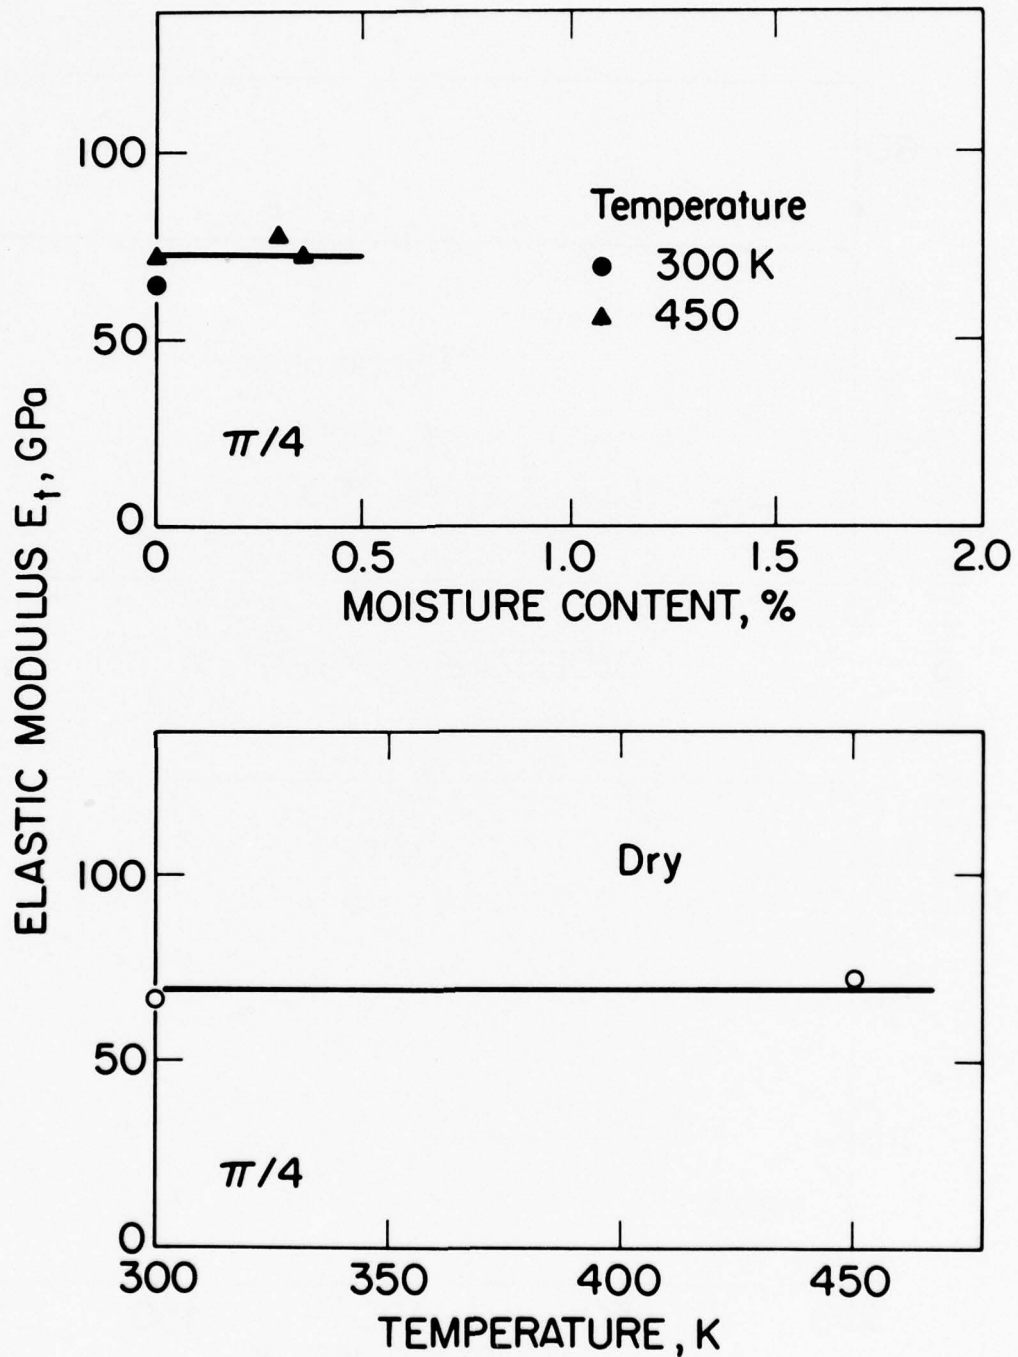


Figure 12. Quasi-Isotropic Tensile Modulus of HT-S/Fiberite X-911 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11].

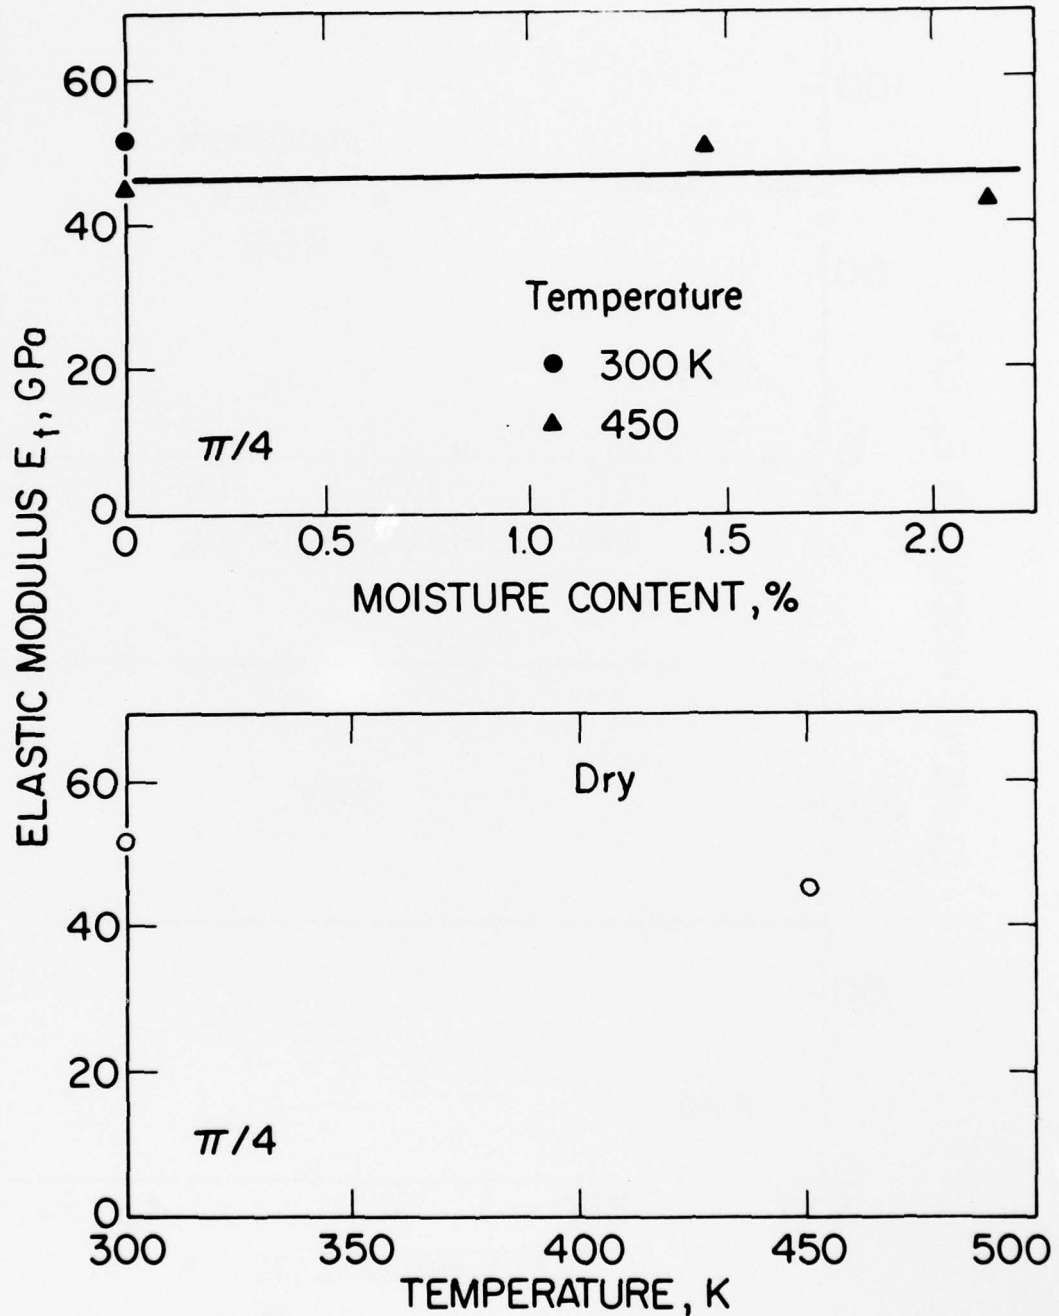


Figure 13. Quasi-Isotropic Tensile Modulus of HT/S/UCC X-2546 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11].

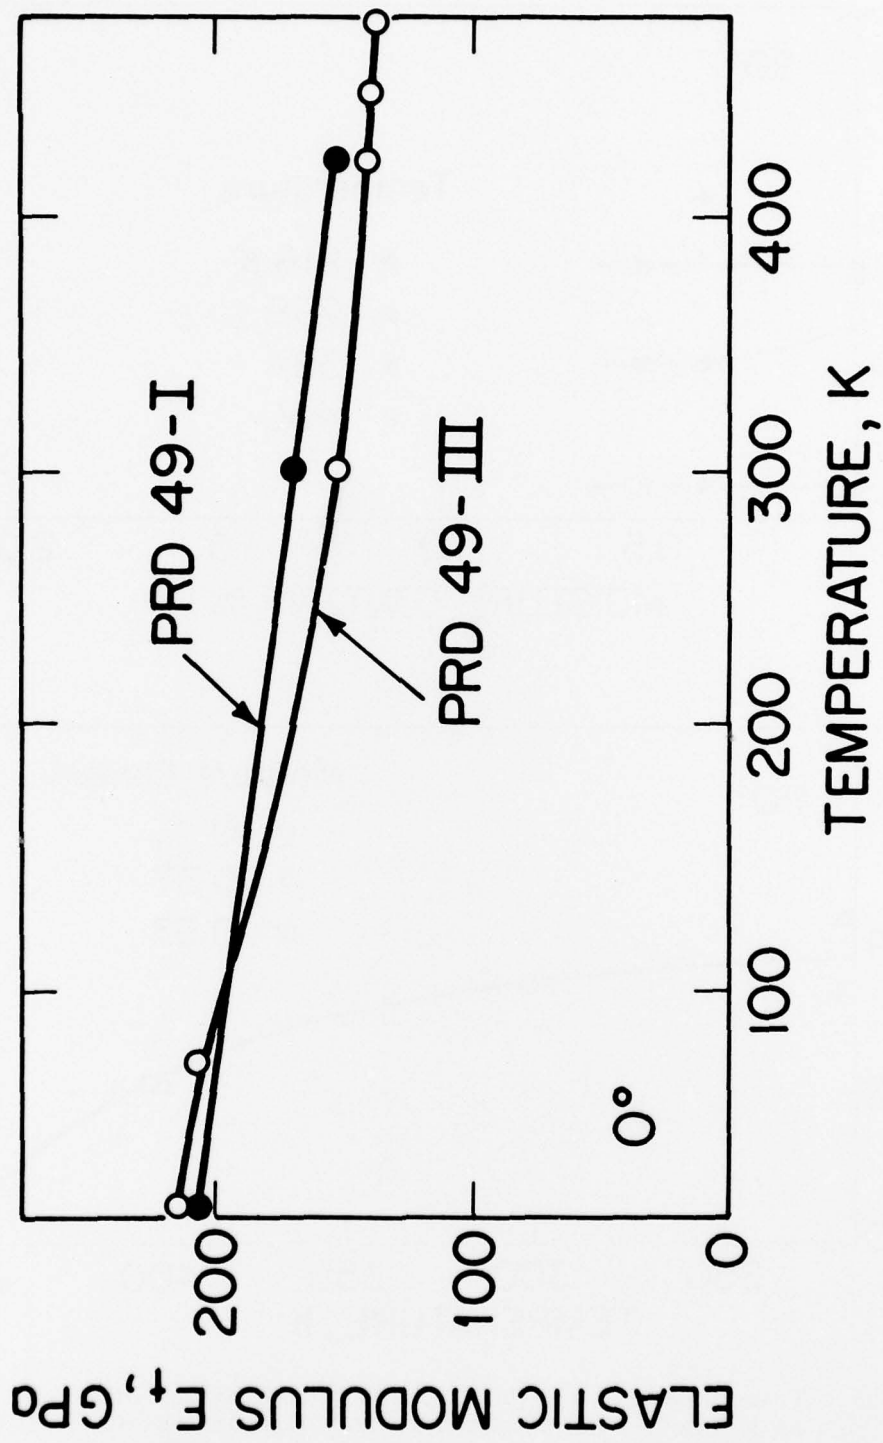


Figure 14. Dry Longitudinal Tensile Modulus of PRD-49/ERLB-4617 as a Function of Temperature. Data of Hanson, 1972 [12].

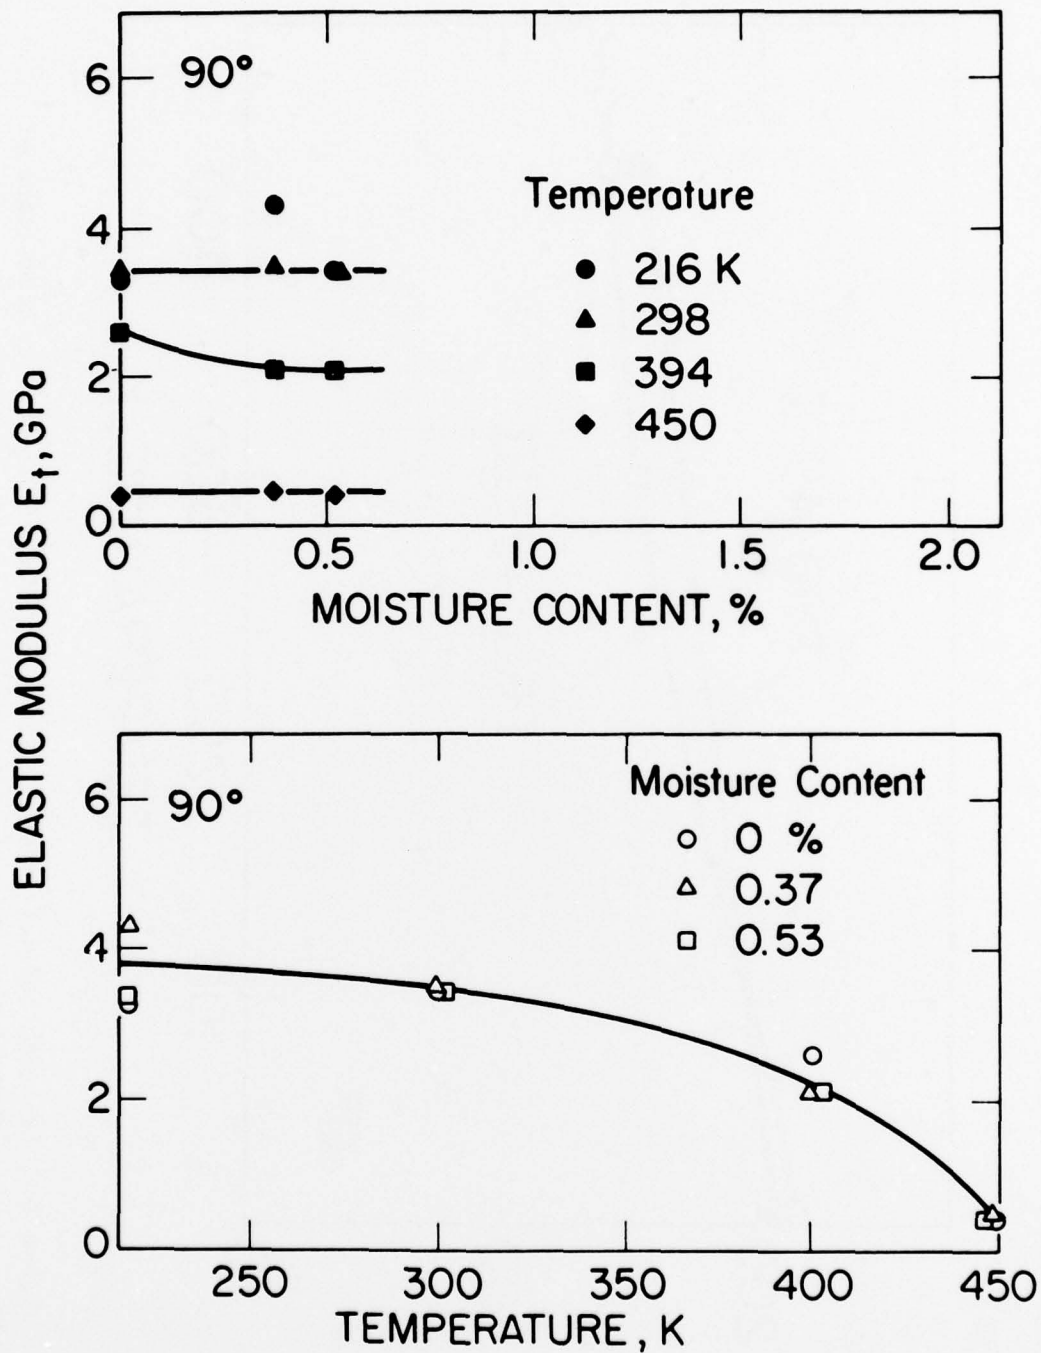


Figure 15. Transverse Tensile Modulus of HT-S/(8183/137-NDA-BF₃: MEA) as a Function of Temperature and Moisture Content. Data of Hertz, 1973 [13].

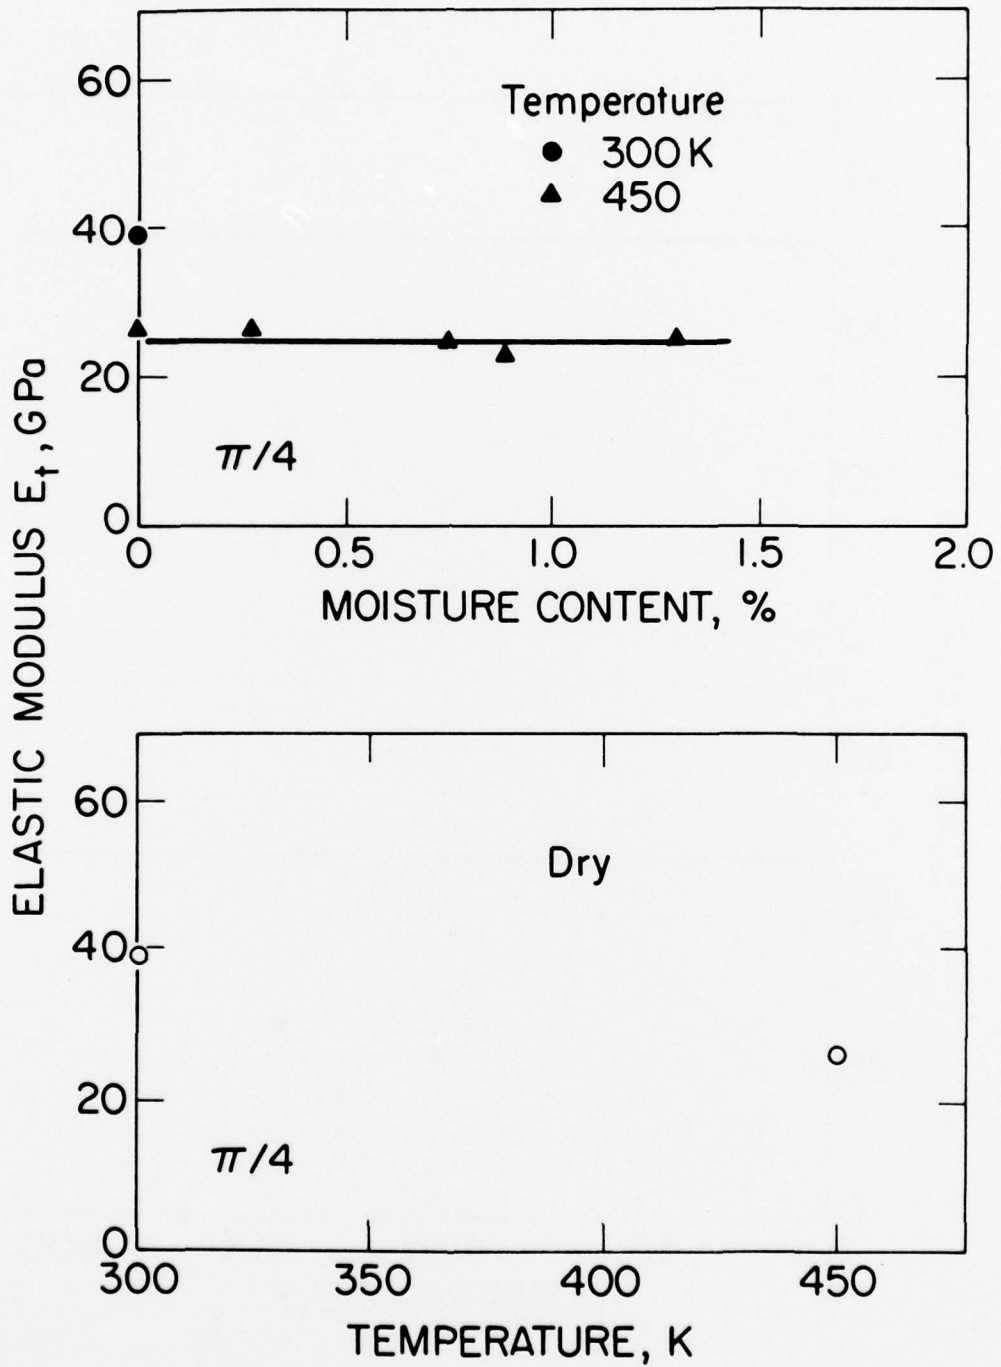


Figure 16. Quasi-Isotropic Tensile Modulus of HT/S/Hysol ADX-516 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11].

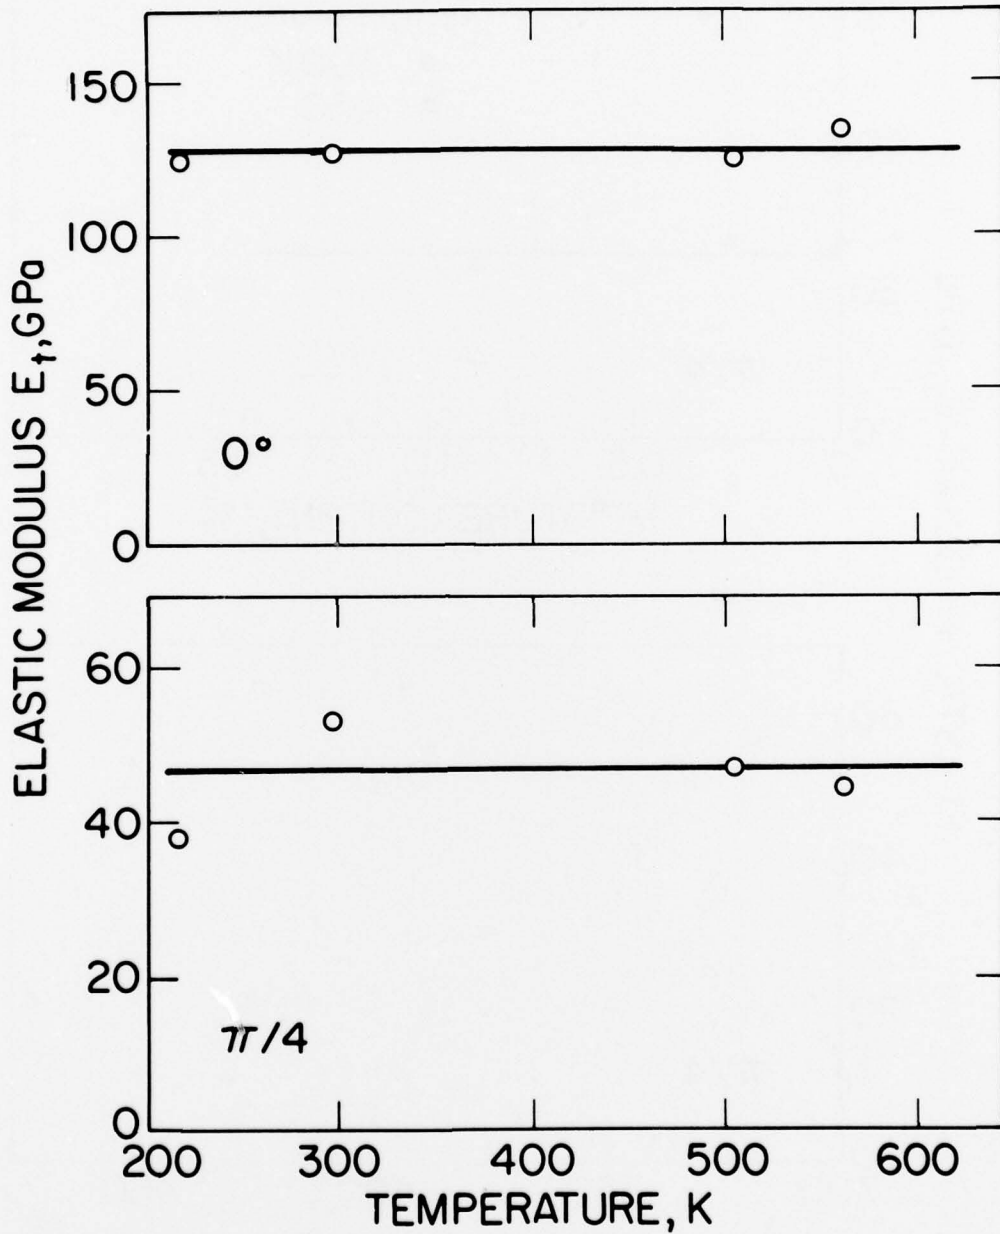


Figure 17. Dry Longitudinal and Quasi-Isotropic Tensile Moduli of HT-S/710 Polyimide as a Function of Temperature. Data of Kerr, et al. 1975 [7].

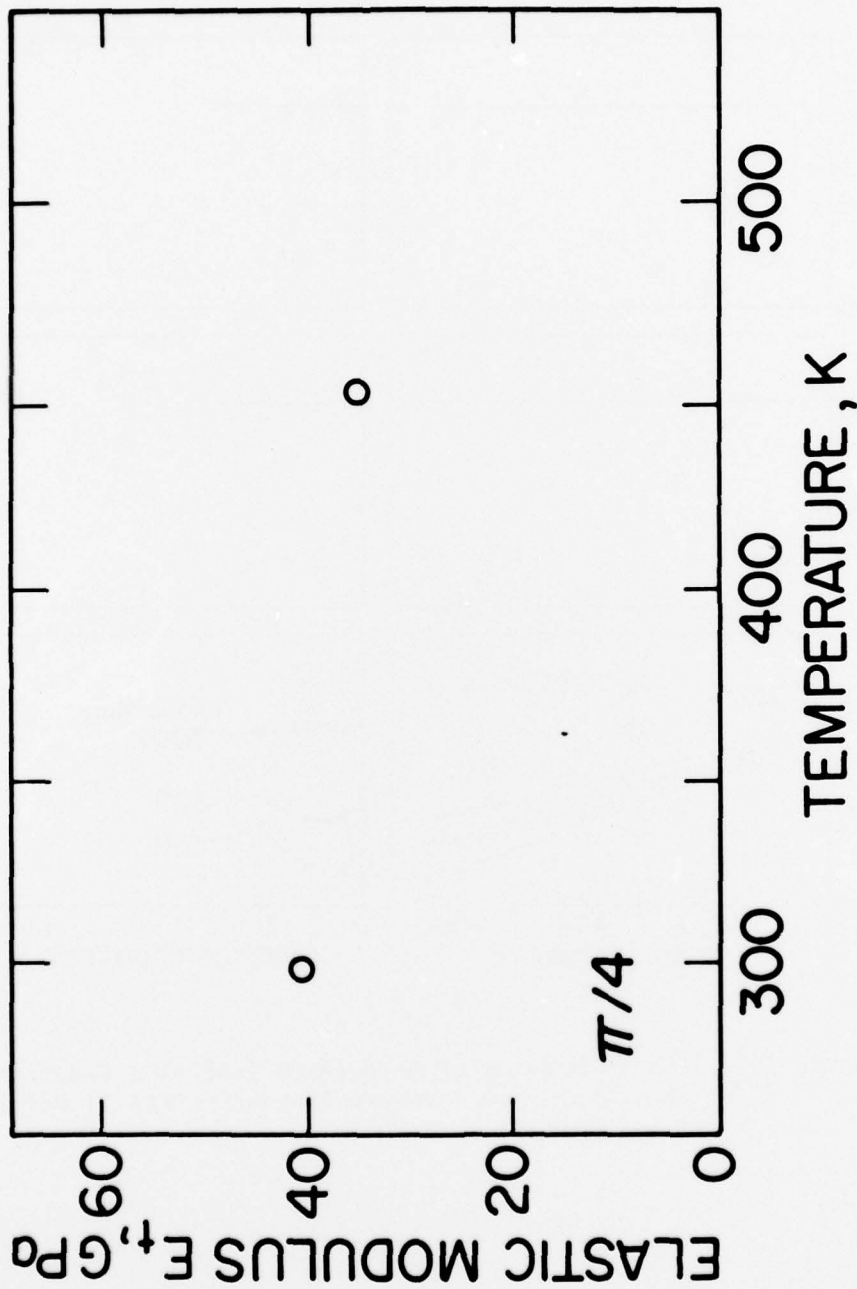


Figure 18. Dry Quasi-Isotropic Tensile Modulus of HT-S/P13H Polyimide as a Function of Temperature. Data of Browning, 1972 [11].

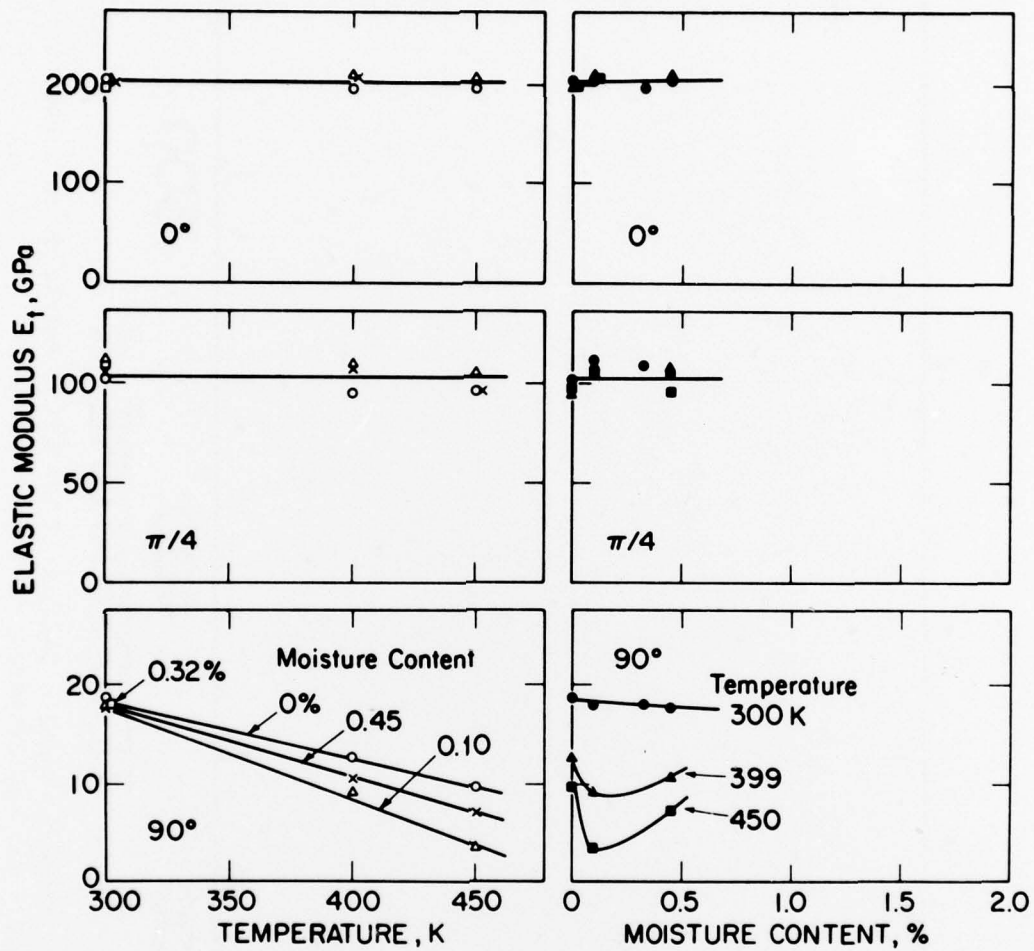


Figure 19. Tensile Modulus of Boron/AVCO 5505 as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10].

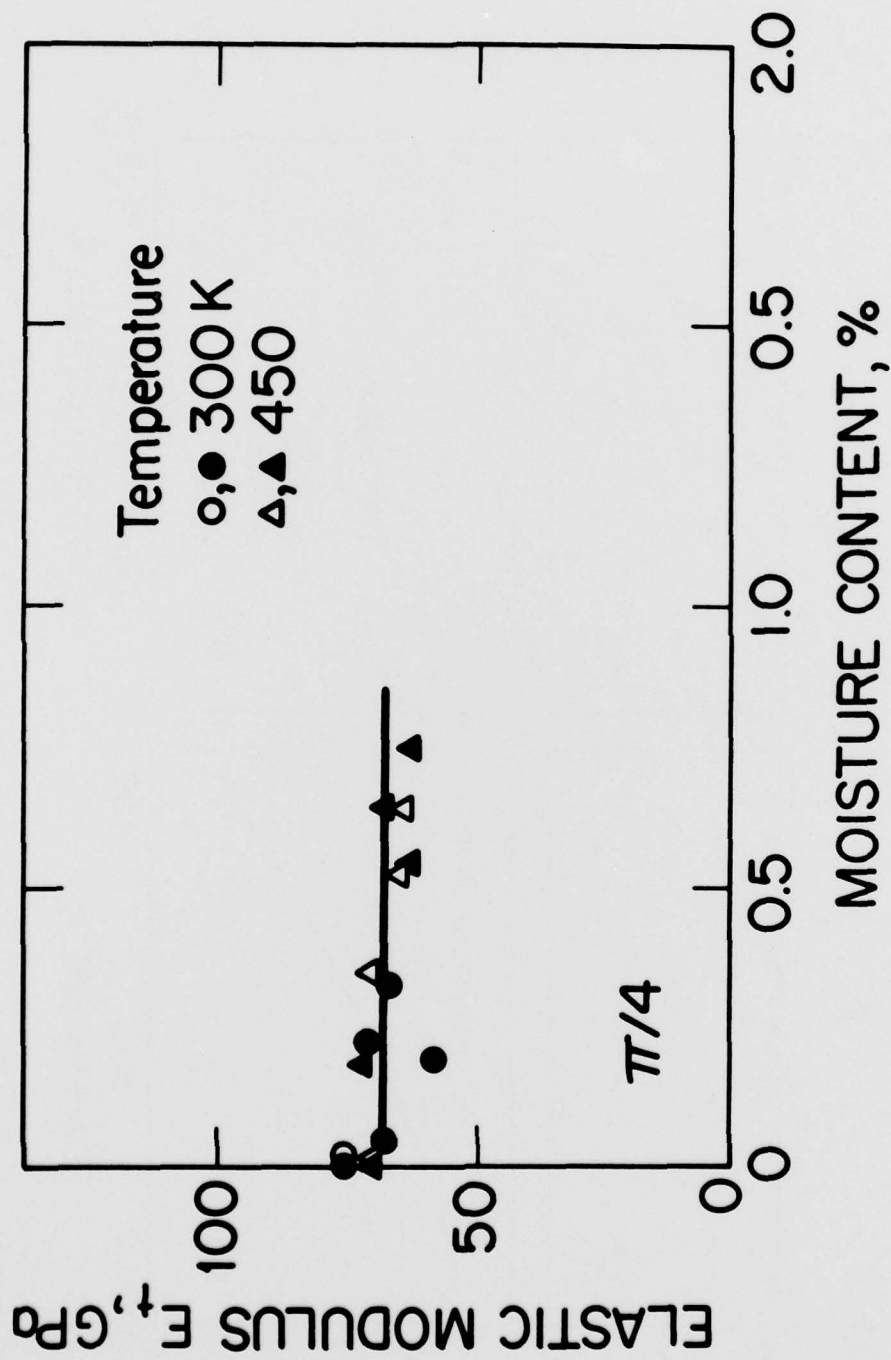


Figure 20. Quasi-Isotropic Tensile Modulus of Boron/Narmco 5505 as a Function of Temperature and Moisture Content. Data of Browning, 1972 [11]. ○ △ : Post-Cured Specimen; ● ▲ : Not Post-Cured Specimen.

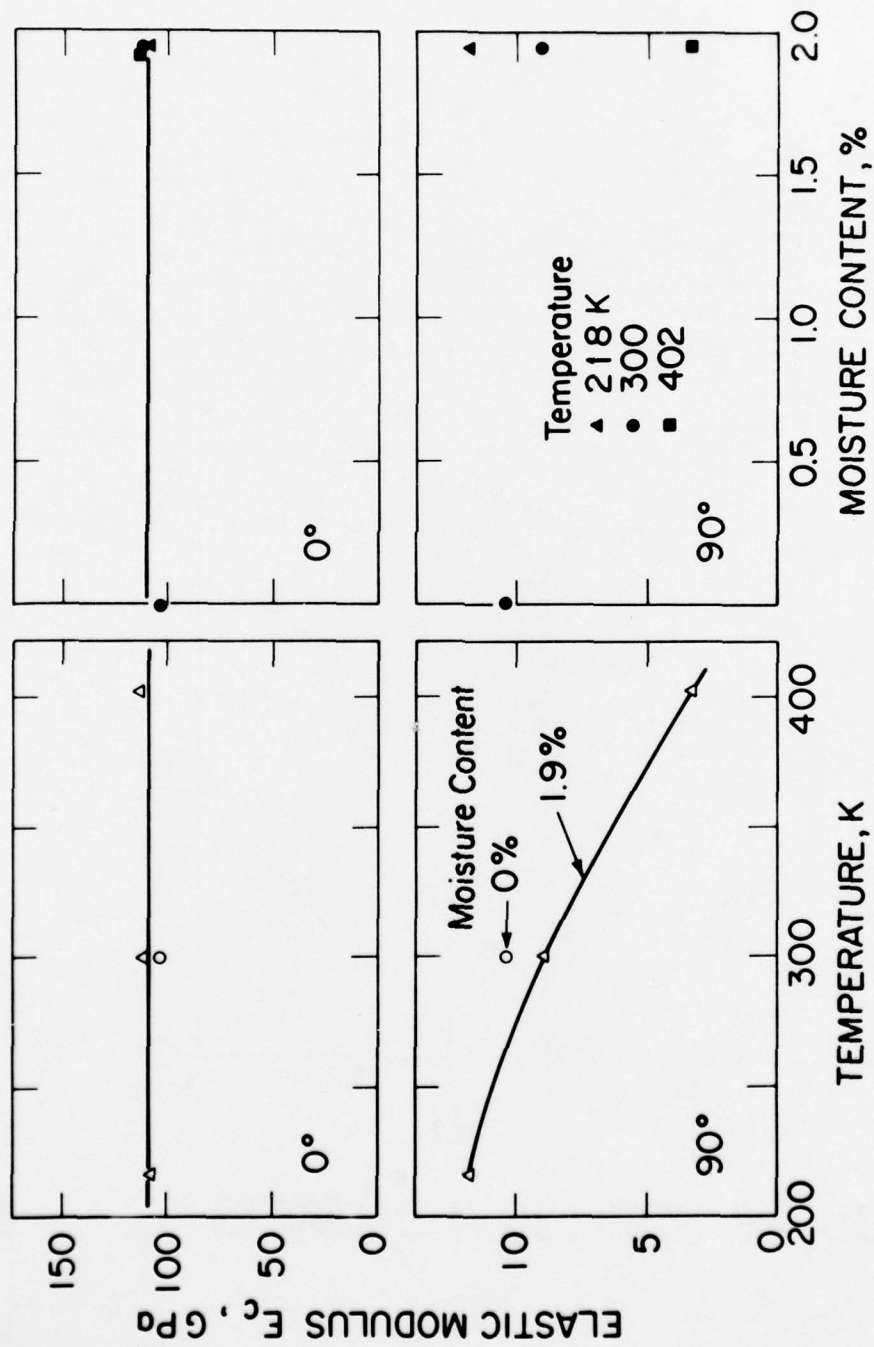


Figure 21. Longitudinal and Transverse Compressive Moduli of Hercules HS-5/3501 as a Function of Temperature and Moisture Content. Data of Verette, 1975 [6].

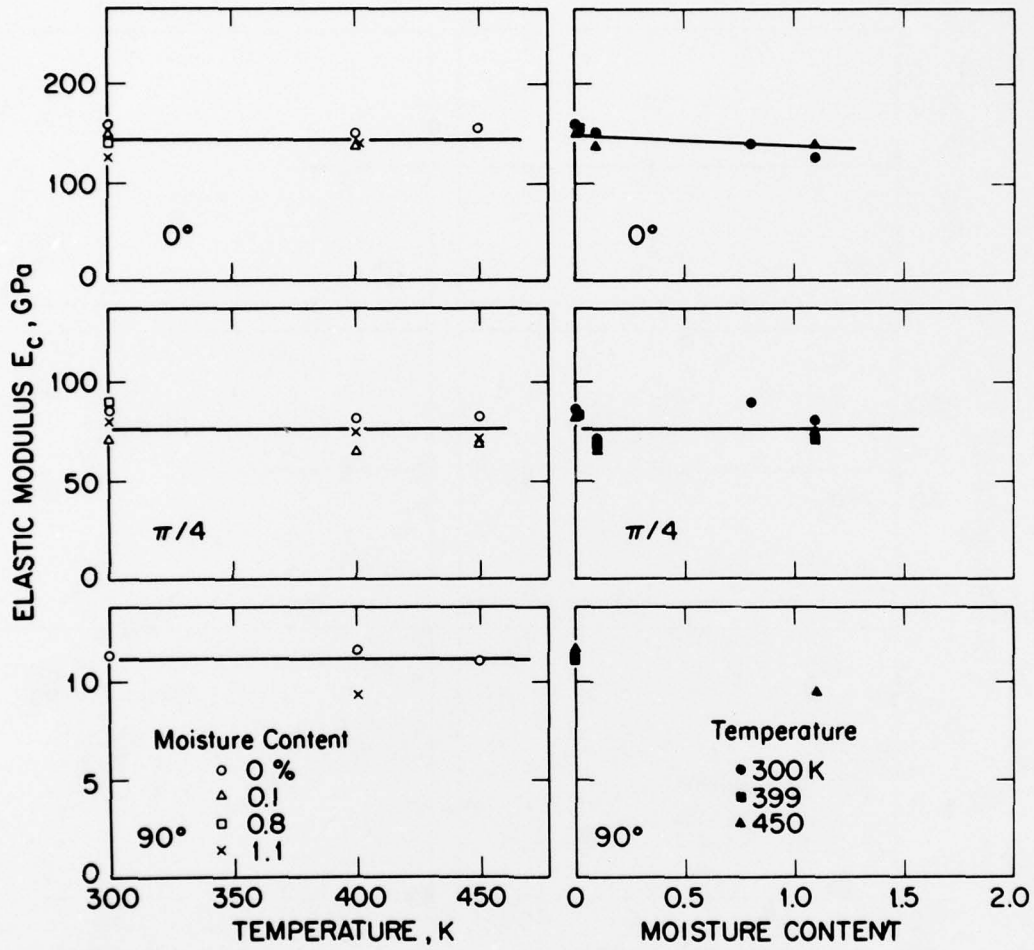


Figure 22. Compressive Modulus of Thornel 300/Narmco 5208 as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1975 [8].

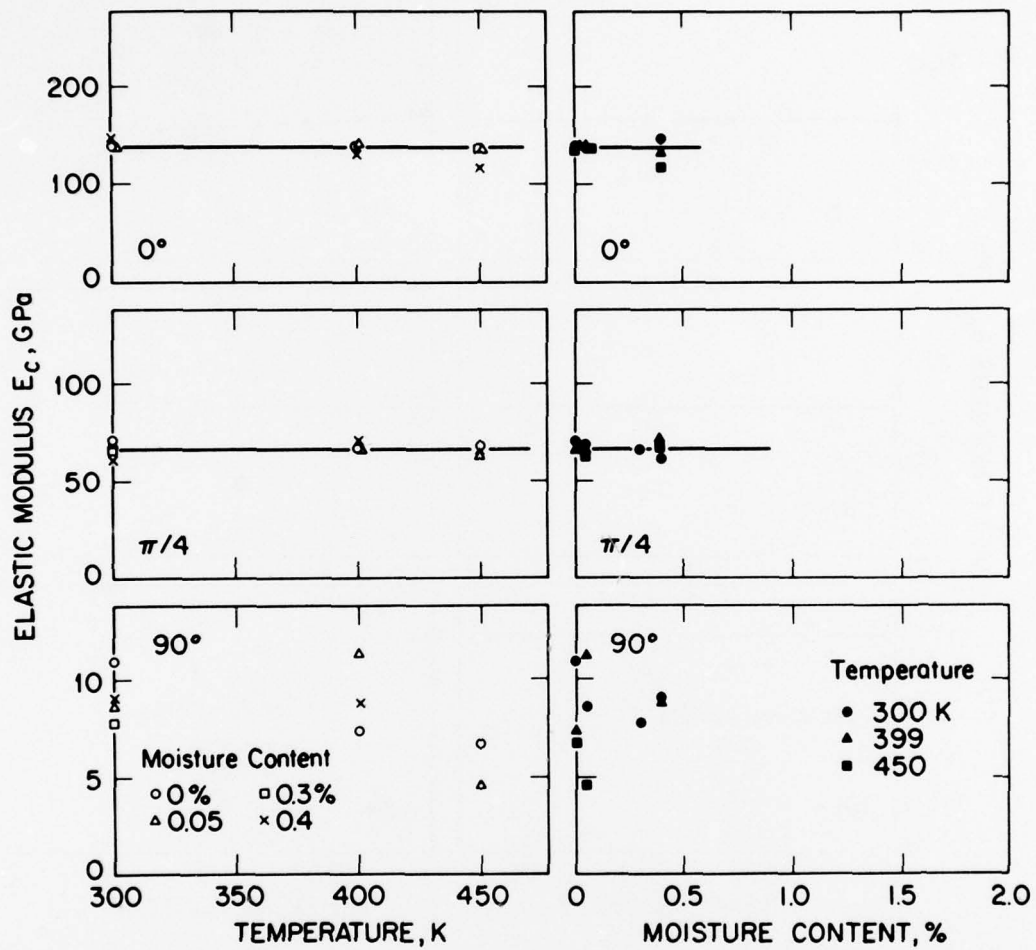


Figure 23. Compressive Modulus of Modmor II/Narmco 5200 as a Function of Temperature and Moisture Content. Data of Hofer, et al., 1974 [10].

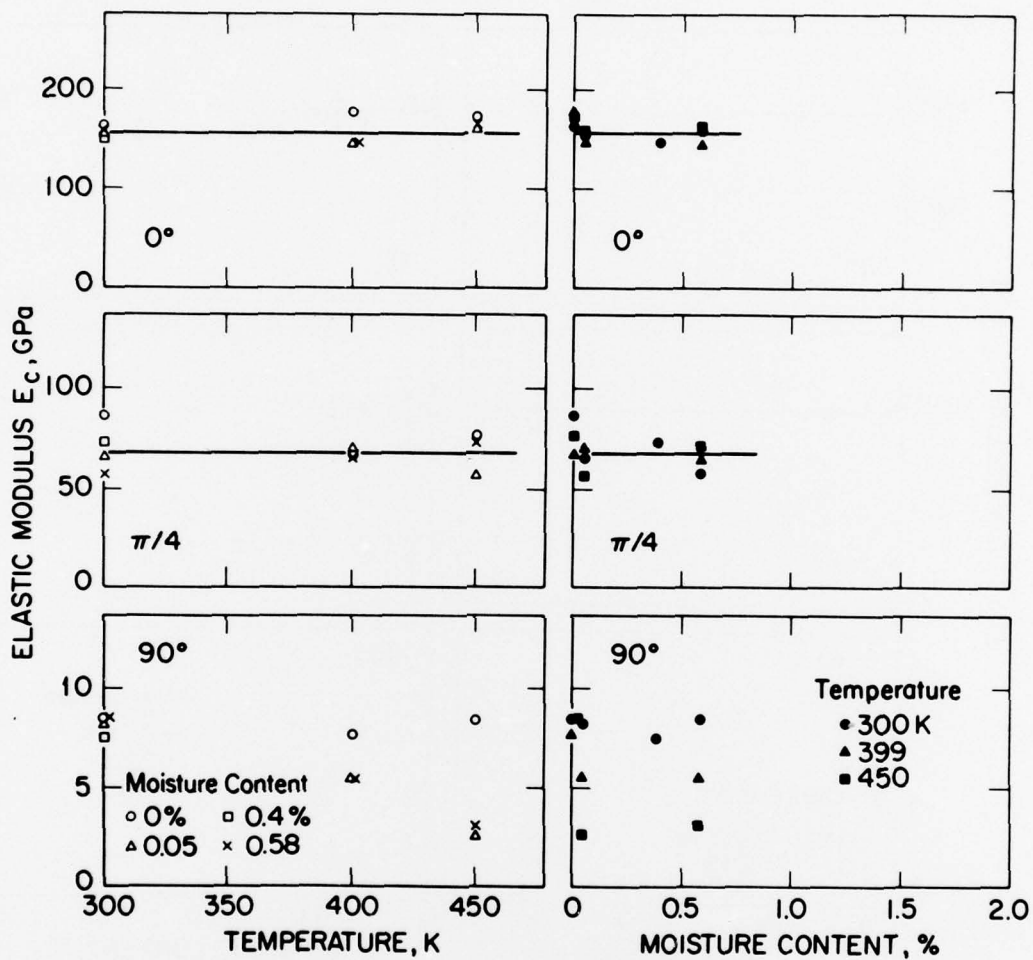


Figure 24. Compressive Modulus of Courtaulds HMS/Hercules 3002M as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10].

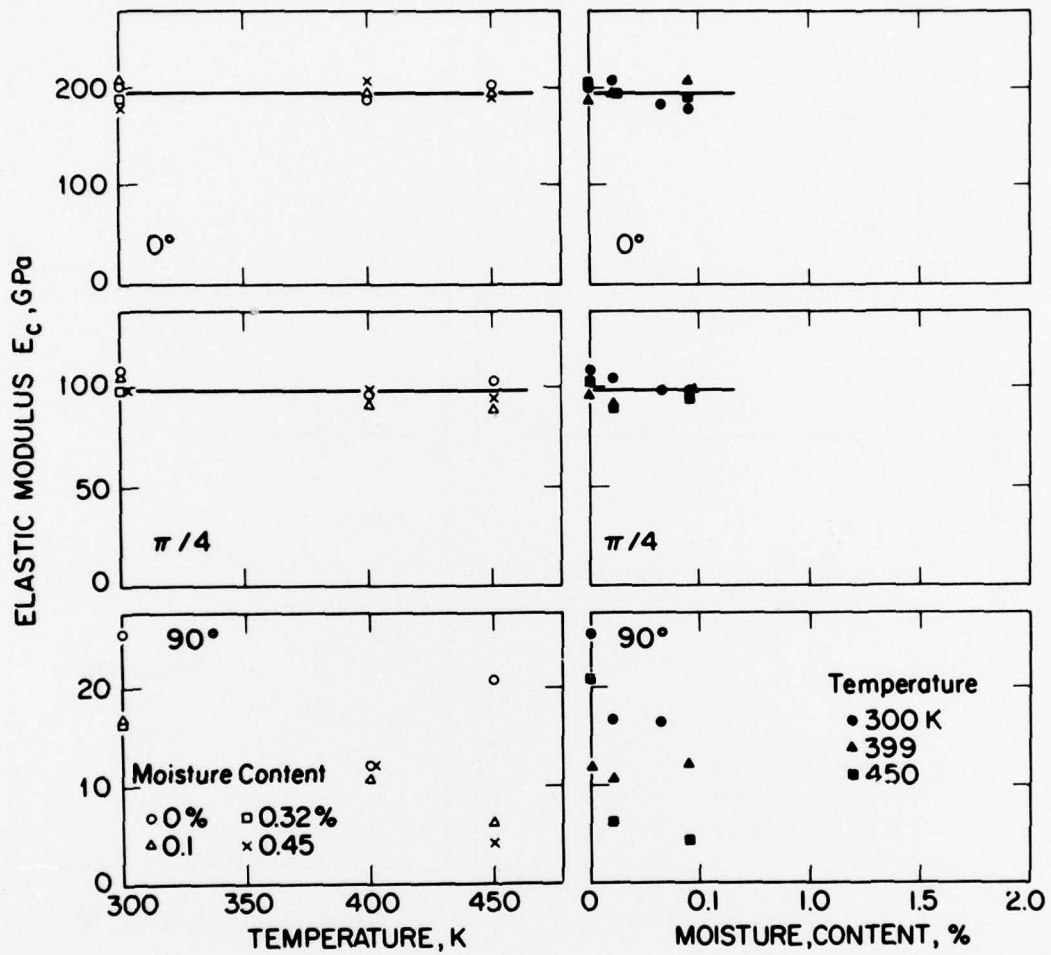


Figure 25. Compressive Modulus of Boron/AVCO 5505 as a Function of Temperature and Moisture Content. Data of Hofer, et al. 1974 [10].

REFERENCES

1. C.H. Shen and G.S. Springer, "Effects of Moisture and Temperature on the Tensile Strength of Composite Materials," *J. Composite Materials*, Vol. 11 (1977), p. 2.
2. G.S. Springer and C.H. Shen, "Moisture Absorption and Desorption of Composite Materials," Technical Report AFML-TR-76-102, June 1976, Air Force Materials Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Dayton, Ohio.
3. A. Chajes, Principles of Structural Stability Theory, Prentice-Hall (1974).
4. C.H. Shen and G.S. Springer, "Moisture Absorption and Desorption of Composite Materials," *J. Composite Materials*, Vol. 10 (1976), p. 2.
5. C.E. Browning, G.E. Husman, and J.M. Whitney, "Moisture Effects in Epoxy Matrix Composites," Composite Materials: Testing and Design, ASTM, STP 617 (1976).
6. R.M. Verette, "Temperature/Humidity Effects on the Strength of Graphite/Epoxy Laminates," AIAA Paper No. 75-1011, AIAA 1975 Aircraft Systems and Technology Meeting, Los Angeles, California, August 4-7, 1975.
7. J.R. Kerr, J.F. Haskins and B.A. Stein, "Program Definition and Preliminary Results of a Long-Term Evaluation Program of Advanced Composites for Supersonic Cruise Aircraft Applications," Environmental Effects on Advanced Composite Materials, ASTM, STP 602 (1975), p. 3.
8. K.E. Hofer, Jr., D. Larsen and V.E. Humphreys, "Development of Engineering Data on the Mechanical and Physical Properties of Advanced Composite Materials," Technical Report AFML-TR-74-266, February, 1975, Air Force Materials Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Dayton, Ohio.
9. G.E. Husman, "Characterization of Wet Composite Materials," Presented at the Mechanics of Composites Review, Bergamo Center, Dayton, Ohio, January 28-29, 1976.
10. K.E. Hofer, Jr., N. Rao and D. Larsen, "Development of Engineering Data on the Mechanical and Physical Properties of Advanced Composite Materials," Technical Report AFML-TR-72-205 Part II, February 1974, Air Force Materials Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Dayton, Ohio.
11. C.E. Browning, "The Effects of Moisture on the Properties of High Performance Structural Resins and Composites," Technical Report AFML-TR-72-94, September 1972, Air Force Materials Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Dayton, Ohio.

12. M.P. Hanson, "Effect of Temperature on the Tensile and Creep Characteristics of PRD 49 Fiber/Epoxy Composites," Composite Materials in Engineering Design, B.R. Norton ed., Proceedings of 6th St. Louis Symposium, May 11-12, 1972, p. 717. Published by The American Society for Metals.

13. J. Hertz, "Investigation into the High-Temperature Strength Degradation of Fiber-Reinforced Resin Composite During Ambient Aging," Convair Aerospace Division, General Dynamics Corporation, Report No. GDCA-DBG73-005, Contract NAS8-27435, June 1973.