

AD-A063 122

OGDEN AIR LOGISTICS CENTER HILL AFB UTAH PROPELLANT L--ETC F/G 21/9.2
SURVEILLANCE REPORT. STAGE I DISSECTED MOTORS. PHASE X. PROPELL--ETC(U)
NOV 78 J A THOMPSON


UNCLASSIFIED

MANCP-406(74)

NL

1 OF 2
AD A063 122



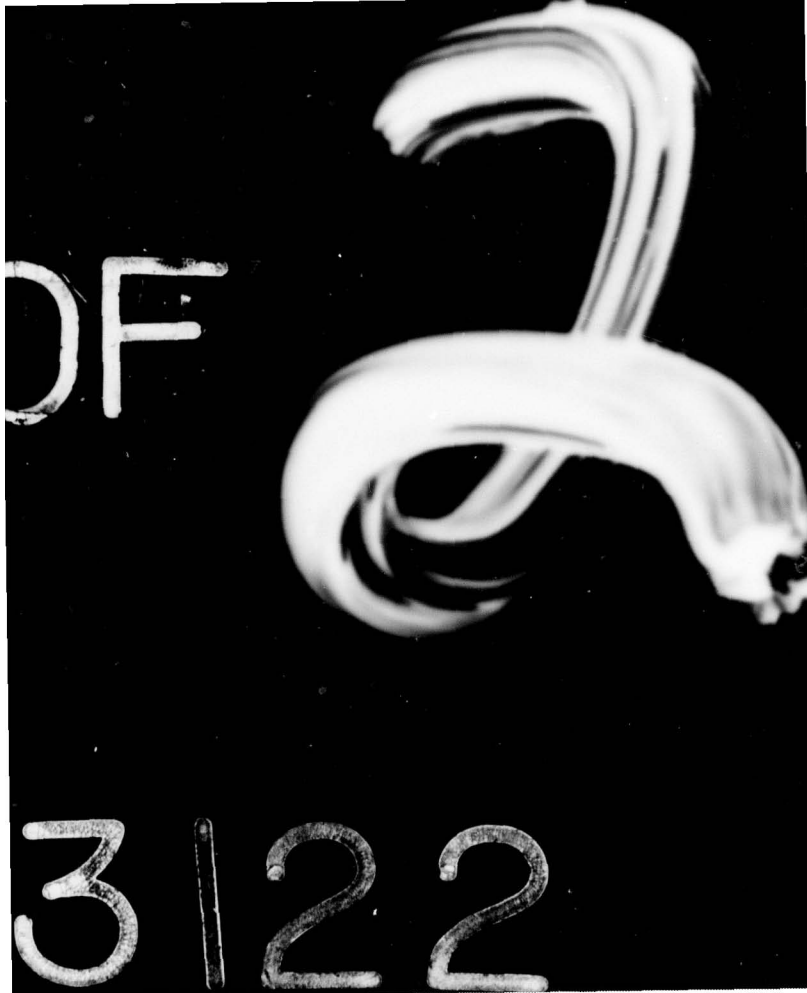

DDC FILE COPY ADA063122

LEVEL II

②
5

HEADQUARTERS

OGDEN AIR LOGISTICS CENTER

UNITED STATES AIR FORCE

HILL AIR FORCE BASE, UTAH 84056

⑥

SURVEILLANCE REPORT.

STAGE I

DISSECTED MOTORS.

PHASE X.

PROPELLANT AND COMPONENT TESTING

⑭ MANCP-406(74)

PROPELLANT LAB SECTION

⑫ 96p.

MANCP REPORT NR
406(78)

⑩ John A. Thompson

DDC
RECEIVED
10 JAN 1979
E

⑪ NOV 1978

APPROVED FOR PUBLIC RELEASE, DISTRIBUTION UNLIMITED

407 387

79 01 10 020

JOB

SURVEILLANCE QUARTERLY REPORT
STAGE I DISSECTED MOTORS
PHASE X PROPELLANT & COMPONENT TESTING

Author

John A. Thompson
JOHN A. THOMPSON, Chemist
Component & Combustion Test Unit

Engineering & Statistical Review By

John K. Scambia
JOHN K. SCAMBIA, Project Engineer
Service Engineering

Edward J. Erickson
EDWARD J. ERICKSON, Statistician
Data Analysis Unit

Recommended Approval By

Ronald F. Larsen
RONALD F. LARSEN, Chief
Physical & Mechanical Test Unit

Leonidas A. Brown
LEONIDAS A. BROWN, Chief
Component & Combustion Test Unit

Approved By

Don F. Woods
DON F. WOODS, Chief
Propellant Laboratory Section

Nov 1978

Industrial Products & Ldg Gear Division
Directorate of Maintenance
Ogden Air Logistics Center
United States Air Force
Hill Air Force Base, Utah 84056

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DDC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION _____	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	_____
A	

ABSTRACT

Testing was performed to determine the useful shelf/service life for LGM-30 Stage I Rocket Motors. A three year storage program for propellant and components was started in May 1961. This program was then extended to a ten year study and later continued indefinitely to assure that a deterioration in motor physical characteristics could be detected in time to take some corrective actions before the weapon system performance deteriorated below an acceptable level.

This report covers only propellant data and limited case bond data. The malfunction of an environmental chamber destroyed component samples that had originally been part of this testing program (and the inadvertent burning of some motors during dissection reduced the material available for testing). Planned dissection of selected motors in the future will provide samples for continued component testing. Test specimens for this reporting period were obtained from motors STM-012, 0012099, 0012199 and UP7775 block propellant.

Separate analyses were made on the respective motors and block propellant for the second time in this report and are shown in the regressions. The plotting symbols for each motor and block propellant are listed in the statistical analyses section.

The data from this test period was combined with data from previous testing and entered into the G085 computer for storage, analysis, and regression analysis. From the statistical analysis of all data tested to date, significant degradation of the propellant does not appear likely for at least two years past the oldest data point.

Future testing will be conducted on dissected motors.

TABLE OF CONTENTS

	<u>Page</u>
Abstract	ii
List of Figures	iv
Glossary of Terms and Abbreviations	vii
Introduction	1
Table 1, Test Program	3
Statistical Approach	5
Test Results	7
Conclusions	10
Recommendations	11
Distribution List	85
DD1473	86

01-10 026

LIST OF FIGURES

<u>Figure Nr</u>		<u>Page</u>
Regression Plot, Low Rate Tensile, 2 in/min		
1	Strain at Maximum Stress	13
2	Maximum Stress	14
3	Strain at Rupture	15
4	Stress at Rupture	16
5	Modulus	18
Regression Plot, Low Rate Tensile, 20 in/min		
6	Strain at Maximum Stress	20
7	Maximum Stress	21
8	Strain at Rupture	22
9	Stress at Rupture	23
10	Modulus	25
Regression Plot, High Rate Tensile		
11	Strain at Maximum Stress	27
12	Maximum Stress	28
13	Strain at Rupture	29
14	Stress at Rupture	30
15	Modulus	31
Regression Plot, High Rate Triaxial Tensile, 600 psi		
16	Strain at Maximum Stress	33
17	Maximum Stress	34
18	Strain at Rupture	35

LIST OF FIGURES (CONT.)

<u>Figure Nr</u>		<u>Page</u>
19	Stress at Rupture	36
20	Modulus	37
21	Regression Plot, Casebond Tensile	39
	Regression Plot, Creep, 10 lb load	
22	Compliance at 10 sec	41
23	Compliance at 20 sec	42
24	Compliance at 1000 sec	43
25	Compliance at 10,000 sec	45
	Regression Plot, Creep, 12 lb load	
26	Compliance at 10 sec	47
27	Compliance at 20 sec	48
28	Compliance at 1,000 sec	49
29	% Strain at Rupture	51
	Regression Plot, Stress Relaxation 3% Strain	
30	Modulus at 10 sec	53
31	Modulus at 50 sec	54
32	Modulus at 100 sec	55
33	Modulus at 1,000 sec	56
	Regression Plot, Stress Relaxation 5% Strain	
34	Modulus at 10 sec	58
35	Modulus at 50 sec	59
36	Modulus at 100 sec	60
37	Modulus at 1000 sec	61

LIST OF FIGURES (CONT)

<u>Figure Nr</u>		<u>Page</u>
38	Regression Plot, Constant Strain	63
39	Regression Plot, Hardness, Shore A, 10 sec	65
40	Regression Plot, Burn Rate, 500 psi	67
41	Regression Plot, Burn Rate, 1000 psi	69
42	Regression Plot, Heat of Explosion	71
43	Regression Plot, Ignitability	73
	Regression Plot, Differential Thermal Analysis, 12°C rise/min	
44	Endotherm 1	75
45	Exotherm 1	76
46	Ignition Temperature	78
	Regression Plot, Sol Gel	
47	Percent Extractables	80
48	Gel Swell Ratio	81
49	Density	82
50	Crosslink Density	83
	Failure Envelopes	
51	Motor S/N 0012099	84

GLOSSARY OF TERMS AND ABBREVIATIONS

Aging Trend	A change in properties or performance resulting from aging of material or component
CSA	Cross Sectional Area
DB	Dogbone
Degradation	Gradual deterioration of properties or performance
E	Modulus (psi), defined as stress divided by strain along the initial linear portion of the curve.
EB	End Bonded
EGL	Effective Gage Length
em	Strain at maximum stress
er	Strain at rupture
"F" ratio	The ratio of the variance accounted for by the regression function to the random unexplained variance. The regression function having the most significant "F" ratio is used for plotting data. The ratio is also used in detecting significant changes in random variation between succeeding time points
JANNAF	Joint Army, Navy, NASA, Air Force Committee
MANCP	Propellant Lab Section at Ogden Air Logistics Center
Ogden ALC	Ogden Air Logistics Center, Air Force Logistics Command
r or R	The Correlation Coefficient is a measure of the degree of closeness of the linear relationship between two variables
Regression Equation	The general form of the regression equation is $Y = a + bx$
Regression Line	Line representing mean test values with respect to time
S_b	Standard error of estimate of the regression coefficient

GLOSSARY OF TERMS AND ABBREVIATIONS (cont)

S_e or $S_{y.X}$	Standard deviation of the data about the regression line
S_m	Maximum Stress
S_r	Stress at rupture
Standard Deviation (S_y)	Square root of variance
Strain Rate	Crosshead speed divided by the EGL
"t" test	A statistical test used to detect significant differences between a measured parameter and an expected value of the parameter (determines if regression slope differs from zero at the 95% confidence level)
Variance	The sum of squares of deviations of the test results from the mean of the series after division by one less than the total number of test results
3 Sigma Band	The area between the upper and lower 3 sigma limit. It can be expected that 99.73% of the inventory represented by the test samples would fall within this range assuming that the population is normally distributed.
90-90 Band	It can be stated with 90% confidence that 90% of the inventory represented by the test samples would fall within this range assuming that the population is normally distributed

INTRODUCTION

A. PURPOSE:

This report contains test data from samples of LGM-30 Stage I, Wings I-V TP-H1011 propellant and case bond specimens. Testing was performed by the Propellant Laboratory Section (MANCP) for the Engineering and Reliability Branch of the Airmunitions Management Division (MMWRM) under Project M82934C-WNL17514. This report is the tenth in this series. Data from this test period and propellant test data from the nine previous reports were entered into the GO85 computer for regression analysis. The regressions are shown in this report.

B. TEST PROGRAM:

The LGM-30 Laboratory and Component Program includes the testing of materials used in the main case, aft closure, ignition assemblies, and main grain propellant. This report covers TP-H1011 propellant and case bond specimens. Table I outlines the test program.

Propellant for testing was obtained from three dissected motors, STM-012, a motor prepared by Thiokol specifically for dissection; S/N 0012099, A SLIM motor; Motor S/N 0012199 selected from the inventory for dissection; and UP-7775 block propellant.

C. HISTORICAL BACKGROUND:

In May 1961, Thiokol began a three year LGM-30 laboratory storage and test program to determine the rate of degradation with age for Stage I materials. During June 1962 and again in August 1963, additional samples were included. New samples were added in July and August 1964 when the

surveillance testing program was extended to ten years (Test Plan 0717-62-0967, 53-8). Carton block propellant, batch UP-7775, containing TP-H1011 propellant cast in March 1962 was added to the program in 1964.

Samples added to the inventory in 1964 were considered to be a new population, but were combined in regression analysis with the three dissected motors. The history of testing of these materials is found in MQQP Report Nrs. 109A(67), 144(68), 208(71), and MANCP Report 358(76). Physical transfer of the specimens from Thiokol to Ogden ALC was made in June 1967.

TABLE I

TEST PROGRAM

All Temperatures in Fahrenheit

STM-012, SN 0012099, SN 0012199, UP-7775

<u>Test</u>	<u>Conditions</u>	<u>Spec/ Cond</u>	<u>Spec Conf</u>
Tensile	77°, 2.0 & 20 in/min	5 ea	JANNAF Dogbone
Creep	77°, 10 & 12 lb load	3 ea	JANNAF Dogbone
Stress Relax	77°, 3 & 5% strain	3 ea	1/2" x 1/2" x 4"
Strain Dilatation	77°, .25 in/ in/min	3 ea	1/2" x 1/2" x 4"
Hardness	77°, initial & 10 sec	5 ea	Dogbone Ends
HOE	77°	3 ea	1/2" x 3/8" x 1"
Burning Rate	77°, 500 & 1,000 psi	5 ea	.156" x .156" x 5"
DTA	77° start	3 ea	0.040" wafer
Ignitability	77°, 168 cal/ cm ² /sec	3 ea	0.050" wafer
Sol Gel	77°	6 ea	1/2" x 1/2" x 1/2"
UP 7775 will <u>NOT</u> be used on the following tests:			
High rate Tensile	77°, 1,000 in/in/min	5 ea	3/4" GL Dogbone
Triaxial High Rate	77°, 1,000 in/in/min 600 psi	3 ea	3/4" GL Rail
Dynamic Response	77°, 70 gm ct wt	3 ea	3.3" x .33" x 0.690" disc
Biaxial constant Strain	77°	3 ea	3/4" GL Rail

TABLE I (cont)

<u>Test</u>	<u>Conditions</u>	<u>Spec/Cond</u>	<u>Spec Conf</u>
Failure Envelope	Temp: -50° -20°, 10° 40°, 77° 130°, & 180°F at a rate of 0.2, 2.0, & 20 in/min	3 ea	JANNAF Dogbone
STM012 and 0012199 only will be for the following tests:			
Case Bond Tensile	77°, 0.2 in/ min	10 ea	1" x 5/8" x 3/4"
Tear Energy	77°F ± 2°	8 ea	0.1" x 1.18" x 3"
Poisson's Ratio (Strain Dilatation) 10, 15, 20 25, 30%	77°F ± 2°	6 per/ condition	0.50" x 0.50" x 4"

STATISTICAL ANALYSIS

The objective of this statistical analysis is to determine whether or not any aging trends are demonstrated by accumulated test data in order to assist Service Engineering to more accurately predict motor serviceability.

Propellant was made available for testing and statistical analysis to obtain an overall view of the aging trends affecting the First Stage Dissected Motor Program. The sampling consists of data from two dissected operational motors (0012099 and 0012199), and carton propellant (batch UP-7775). One motor (STM-012) was prepared by Thiokol specifically for the dissection program.

A Multi-symbol Regression Analysis Program was used to determine aging trends. The sampling is combined for each test parameter in a single regression analysis. The linear equation ($Y = a + bX$) was found to be the best fit model for the data in this report. A composite population aging trend line is then calculated accepting the fact that individual aging of different populations may be masked.

The Multi-symbol Program uses a unique plotting code for each motor and carton data on the regression plots. This method of data plotting allows a visual display of the overall relationship between the various origins of data and how they relate to the overall least square aging trend line.

The regression program uses an analysis with individual data points from different time periods combined to establish a least squares aging trend line for the overall data. The variance about the regression line, obtained using individual values of the dependent variable, was used to compute a tolerance interval such that at the 90% confidence level 90% of the population falls within this interval. This tolerance interval was

extrapolated to a maximum of 24 months to give an indication of the statistical significance of the slope of any aging trends. The computer tolerance interval about the composite regression line is wider than what the tolerance interval would be about any individual motor or carton regression line because of the increased data spread introduced by combining different populations of data. The "t" values and the significance of this statistic, which are reported for each regression model, gives an indication of the "statistical significance" of the slope of the aging trend in the Y-axis. Data and regression trend lines were plotted utilizing an IBM-360/65 computer.

ORIGIN SYMBOL TABLE

<u>Origin</u>	<u>DOM</u>	<u>Wing</u>	<u>Symbol</u>
Motor 0012099	63166	2	0
Motor 0012199	63227	2	1
Motor STM-012	61221	1	S
Carton UP-7775	62075	1	U

TEST RESULTS

Regression analysis is the method of evaluation used in the analysis of the test results.

A. TENSILE:

Low rate tensile test data shows a statistically significant gradual decrease for strain at maximum stress and strain at rupture. Maximum stress and stress at rupture do not show a significant change. The modulus shows a statistically significant increase. (Figures 1 thru 5).

The 20/min low rate tensile test data shows a statistically significant decrease for the strain at maximum stress, strain at rupture and stress at rupture. Maximum stress and modulus do not show a significant change. (Figures 6 thru 10).

No significant change is shown for the high rate regressions (Figures 11 thru 15).

High rate triaxial testing shows a statistically significant increase for the strains and stress at rupture with the maximum stress showing no significant change. Modulus shows a statistically significant decrease. (Figure 16 thru 20).

Case bond tensile data shows a statistically significant decrease (Figure 21). For this test period, 10 specimens were tested. The failure mode for 5 specimens was 100% adhesive, liner to propellant. Two specimens had 100% adhesive, case to liner failure. Data on three of the specimens was not used. Examination after testing showed up to

90% of the case bond surface area was rusty. The most probable cause for the rusty area would be damage to the case bond when the motor was dissected or when the specimens were machined. There is the possibility that the case was not prepared properly before the liner was applied.

B. CREEP:

For the 10 pound load test data the regressions show a statistically significant decrease, except for the 1000 sec regression which shows no significant change (Figure 22 thru 25).

For the 12 pound load a statistically significant decrease in creep compliance is shown for the 10 and 20 second regressions (Figures 26 and 27). The 1000 second and strain at rupture regressions do not show a significant change (Figures 28 and 29).

C. STRESS RELAXATION:

Stress relaxation modulus for both 3 and 5% strain shows no significant change (Figures 30 thru 37).

D. CONSTANT STRAIN:

A statistically significant decrease is shown for constant strain (Figure 38).

E. SHORE HARDNESS:

The Shore A ten second hardness shows no significant change (Figure 39).

F. BURNING RATE:

A statistically significant decrease is shown for both the 500 and 1,000 psi initial testing (Figures 40 and 41).

G. HEAT OF EXPLOSION:

The heat of explosion does not show a significant change (Figure 42).

H. IGNITABILITY:

No significant change is seen in the data by the regression (Figure 43).

I. DIFFERENTIAL THERMAL ANALYSIS (DTA):

The endotherm does not show a significant change (Figure 44). The exotherm shows a statistically significant decrease and the ignition temperature shows a statistically significant increase (Figures 45 and 46).

J. SOL GEL:

A statistically significant gradual decrease is shown for percent extractable wt. swell ratio, sol gel density, and cross link density (Figures 47 thru 50).

K. FAILURE ENVELOPE:

The failure envelope for motor S/N 0012099 is shown in Figure 51.

CONCLUSIONS

The test results show that, under present storage conditions, some of the physical/mechanical and combustion properties of the propellant indicate statistically significant aging trends. On some regressions where a significant trend is indicated, the slope of the trend line is quite gradual and no operational problems are expected. On other regressions, i.e., triaxial tensile and burning rate, the slope of the trend line appears quite steep although, in reality, the percent change is minor as indicated by the formulas found at the top of each figure. The Y-axis range is automatically varied by the data spread to provide visibility between individual data means. As a result, the range values (on Y-axis) must be considered when visually analyzing regression slopes.

Although some aging trends have been observed, it does not appear that any significant degradation will occur in the propellant within the next two years.

RECOMMENDATIONS

It is recommended that continued testing be conducted on the three dissected motors and UP-7775 block propellant presently being tested and also on those motors selected for testing by Service Engineering. On those motors selected for future dissection, testing will include propellant, casebond and component materials.


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
54.0	26	159.0	24
73.0	24	160.0	5
75.0	2	166.0	5
82.0	5	167.0	5
87.0	5	168.0	16
94.0	16	175.0	8
97.0	7	176.0	3
104.0	5	177.0	5
106.0	5	179.0	8
108.0	5	190.0	3
116.0	5	191.0	5
118.0	5	200.0	3
123.0	4	201.0	3
130.0	5	203.0	5
133.0	15		
135.0	3		
140.0	5		
144.0	5		
145.0	3		
146.0	2		
149.0	3		
150.0	10		
152.0	3		
153.0	5		
157.0	3		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable to figures 1 thru 4.


$Y = ((+2.4422012E-01) + (-1.2411640E-04) * X)$
 F = +1.4400278E+01 SIGNIFICANCE OF F = SIGNIFICANT $G_1 = +2.3807804E-02$
 R = -2.2482318E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +3.2616753E-05$
 t = +3.8052960E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_2 = +2.3240919E-02$
 N = 274 DEGREES OF FREEDOM = 272
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

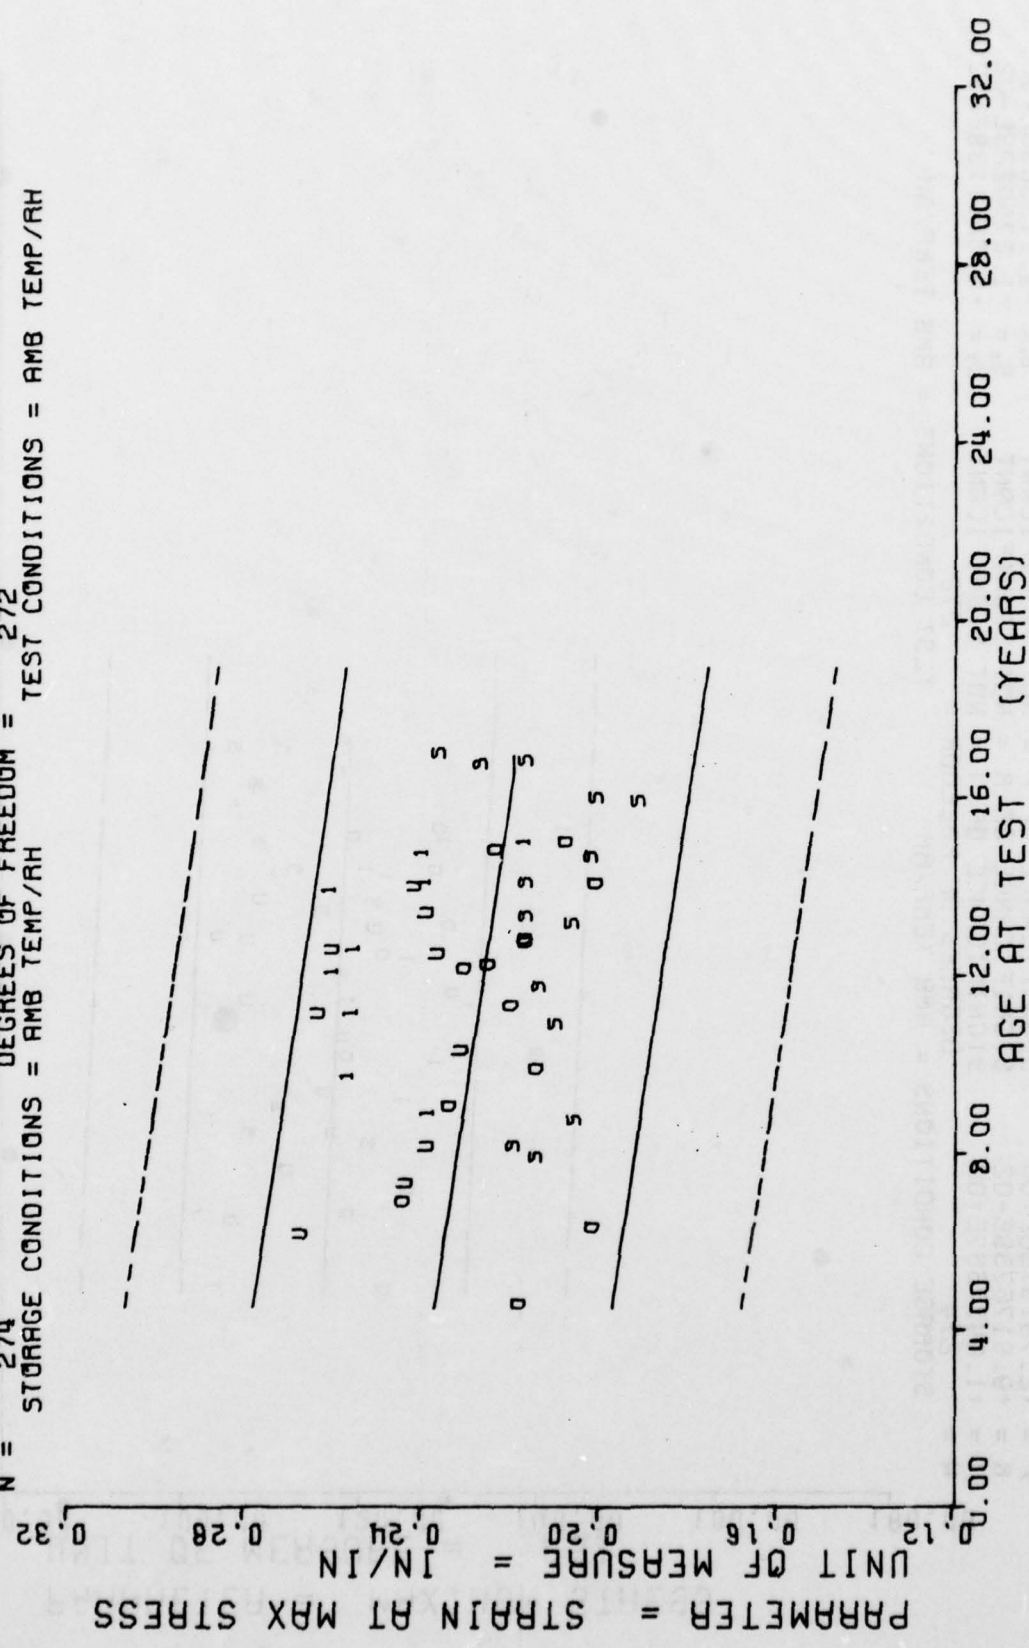

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN MAX STRESS

Figure 1


$Y = ((+1.1494475E+02) + (+2.0958418E-02) * X)$
 F = +2.7019756E+00 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma = +9.1133896E+00$
 R = +9.9176739E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_e = +1.2750223E-02$
 t = +1.6437687E+00 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_r = +9.0851138E+00$
 N = 274 DEGREES OF FREEDOM = 272
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

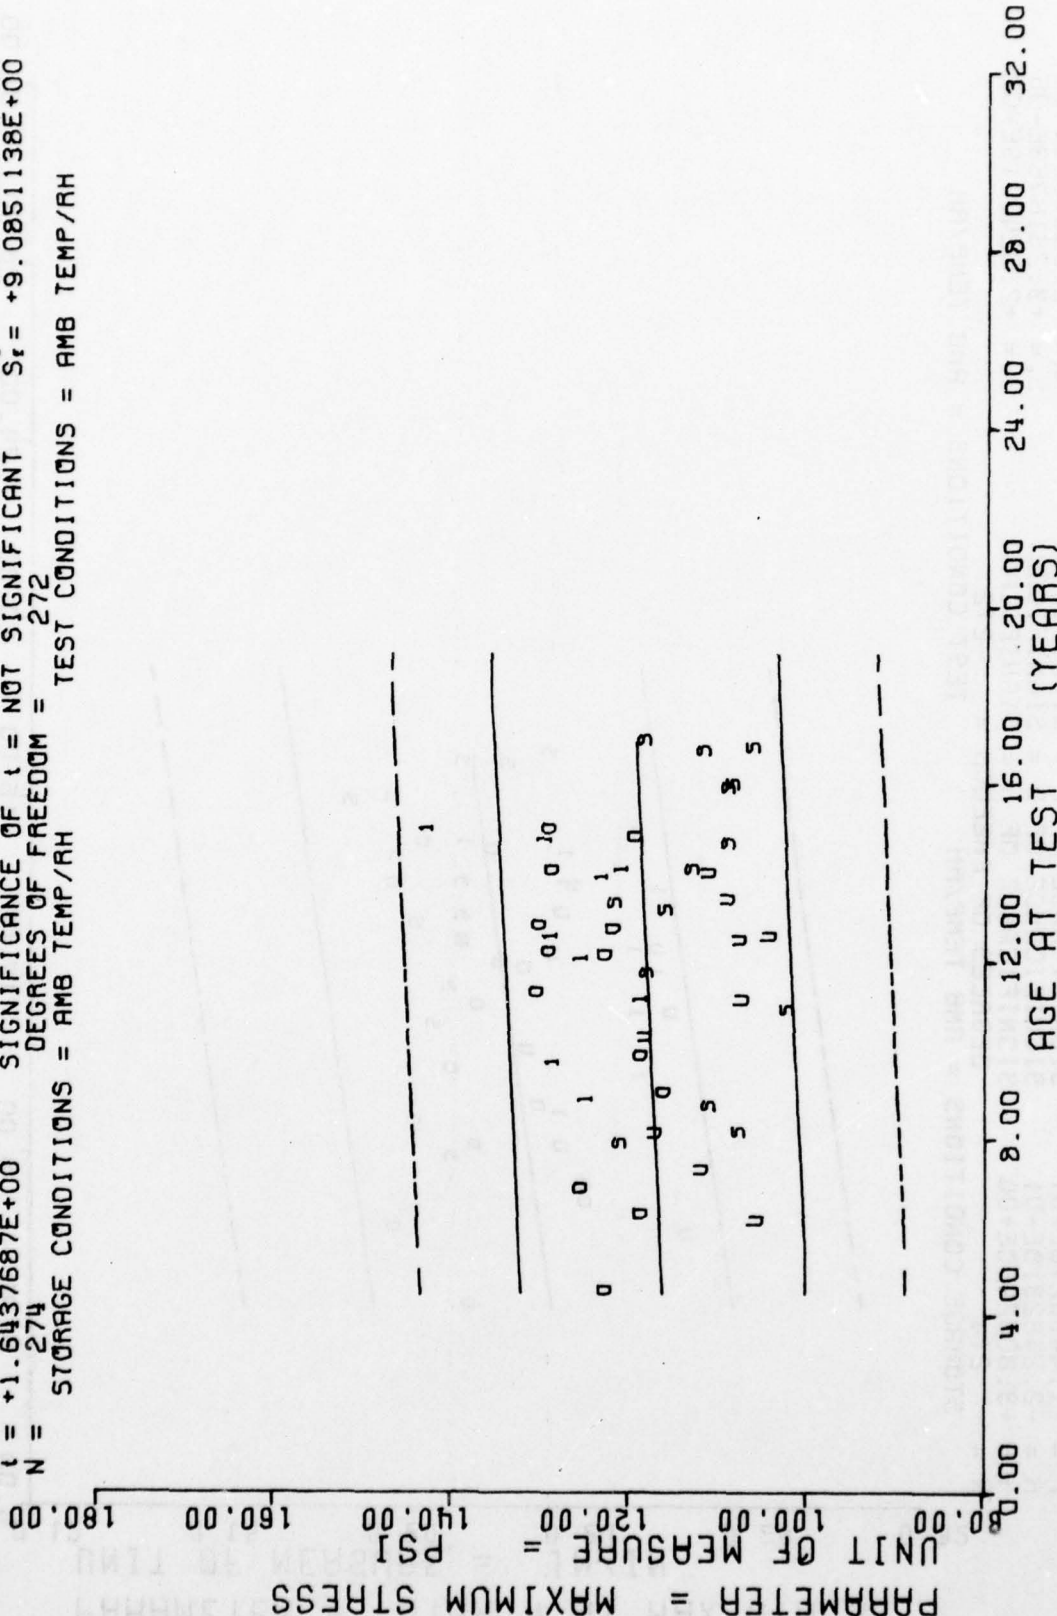

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MAXIMUM STRESS

Figure 2


$Y = ((+3.0558098E-01) + (-1.2085106E-04) * X)$
 F = +9.0065113E+00 SIGNIFICANCE OF F = SIGNIFICANT $\sigma = +2.9111302E-02$
 R = -1.7902764E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_b = +4.0269125E-05$
 t = +3.0010850E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_r = +2.8693582E-02$
 N = 274 DEGREES OF FREEDOM = 272
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 77 DEG/F AMB-RH

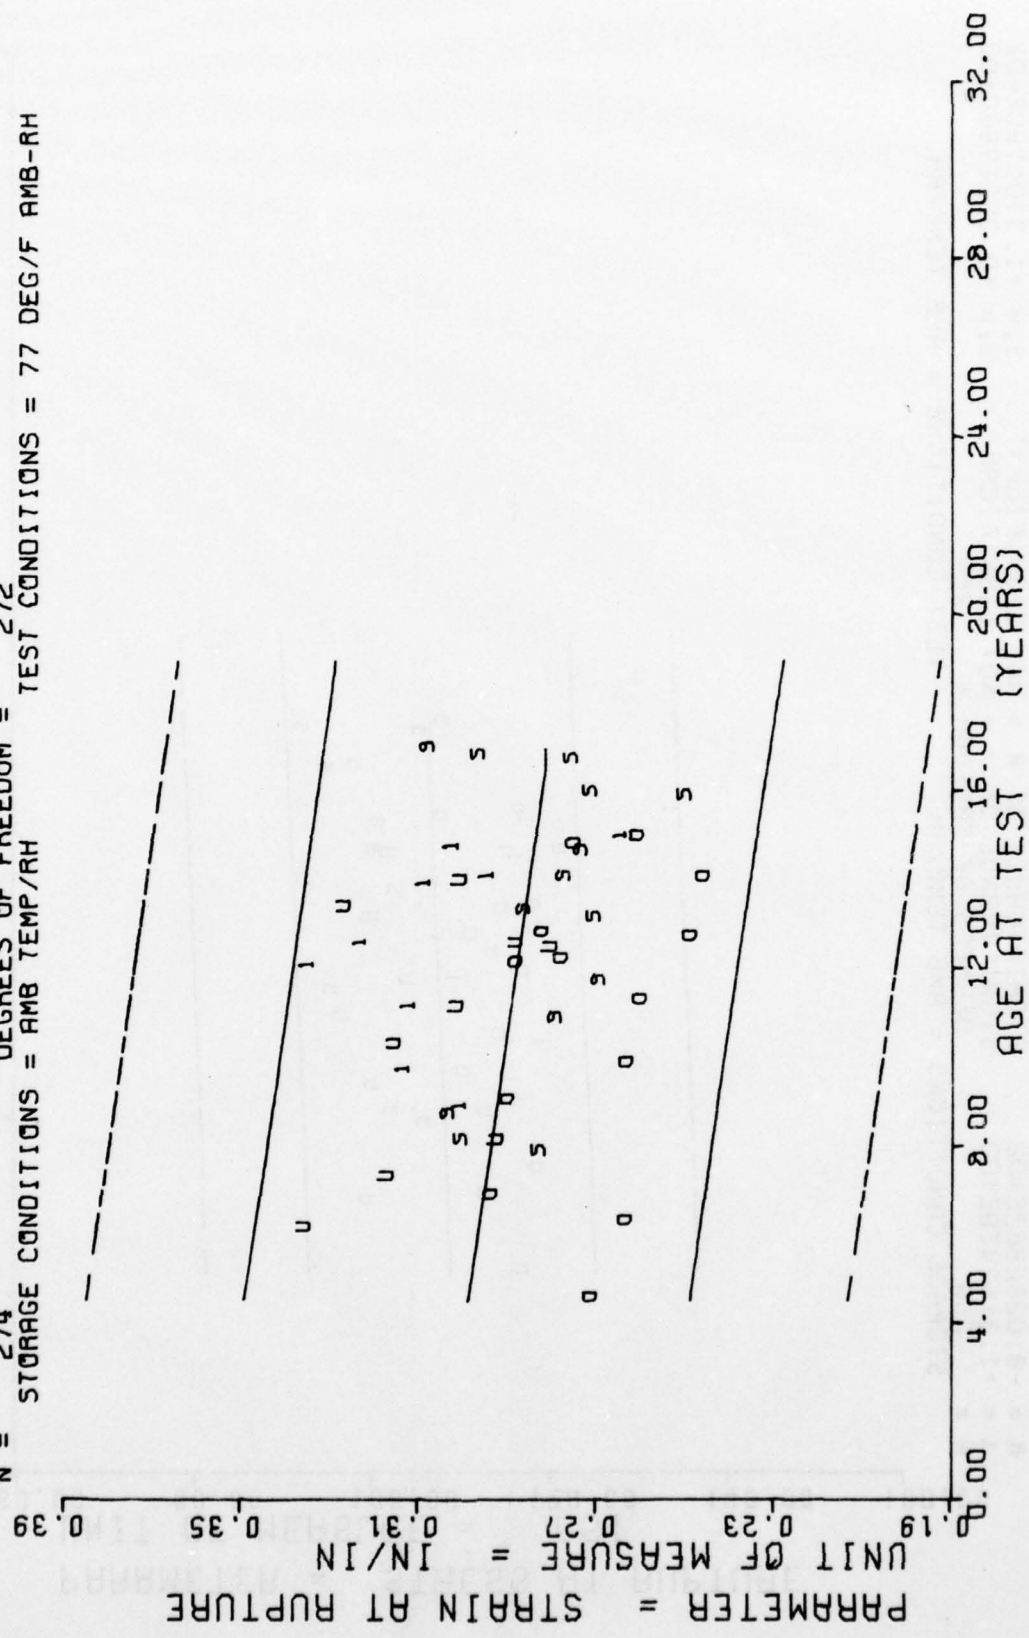

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRAIN AT RUPTURE

Figure 3

$Y = ((+1.1027020E+02) + (-1.7245178E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_f = +9.2648141E+00$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_a = +1.3101790E-02$
 SIGNIFICANCE OF λ = NOT SIGNIFICANT $S_t = +9.2521786E+00$
 N = 269 DEGREES OF FREEDOM = 267
 STORAGE CONDITIONS = AMB TEMP/AH TEST CONDITIONS = AMB TEMP/AH

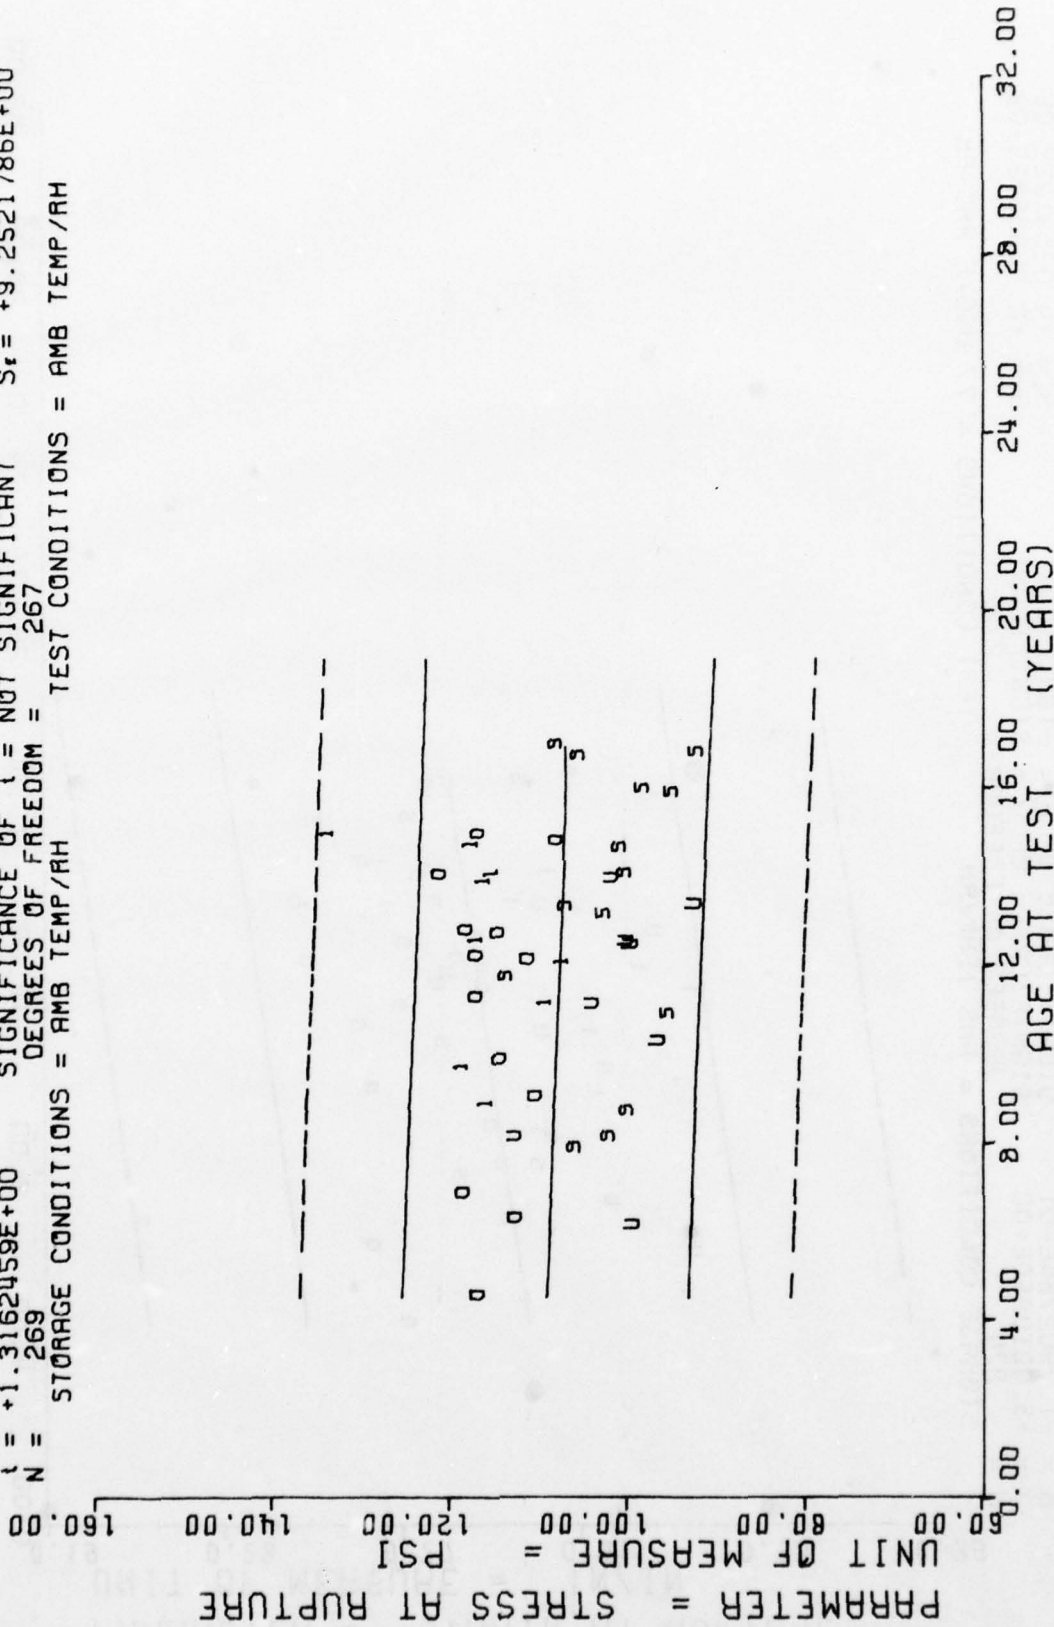

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, STRESS AT RUPTURE

Figure 4


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
54.C	26	168.0	16
73.0	24	175.0	8
82.0	5	176.0	3
87.0	5	177.0	5
94.0	16	179.0	8
97.0	5	190.0	3
104.0	5	191.0	5
106.0	5	200.0	3
108.C	5	201.0	3
123.0	4	203.C	5
130.0	5		
133.0	5		
135.0	3		
144.0	5		
145.0	3		
146.0	2		
149.C	3		
150.0	10		
152.0	3		
153.C	5		
157.0	3		
159.0	24		
160.0	5		
166.0	5		
167.0	5		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MODULUS

This sample size summary is applicable to figure 5.

$Y = ((+9.4969579E+02) + (+1.4077753E+00) * X)$
 $F = +1.7725118E+01$ SIGNIFICANCE OF F = SIGNIFICANT $\sigma_1 = +2.4377791E+02$
 $R = +2.6073728E-01$ SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +3.3437884E-01$
 $t = +4.2101210E+00$ SIGNIFICANCE OF t = SIGNIFICANT $S_t = +2.3582933E+02$
 $N = 245$ DEGREES OF FREEDOM = 243
 STORAGE CONDITIONS = AMB TEMP/AH TEST CONDITIONS = AMB TEMP/AH

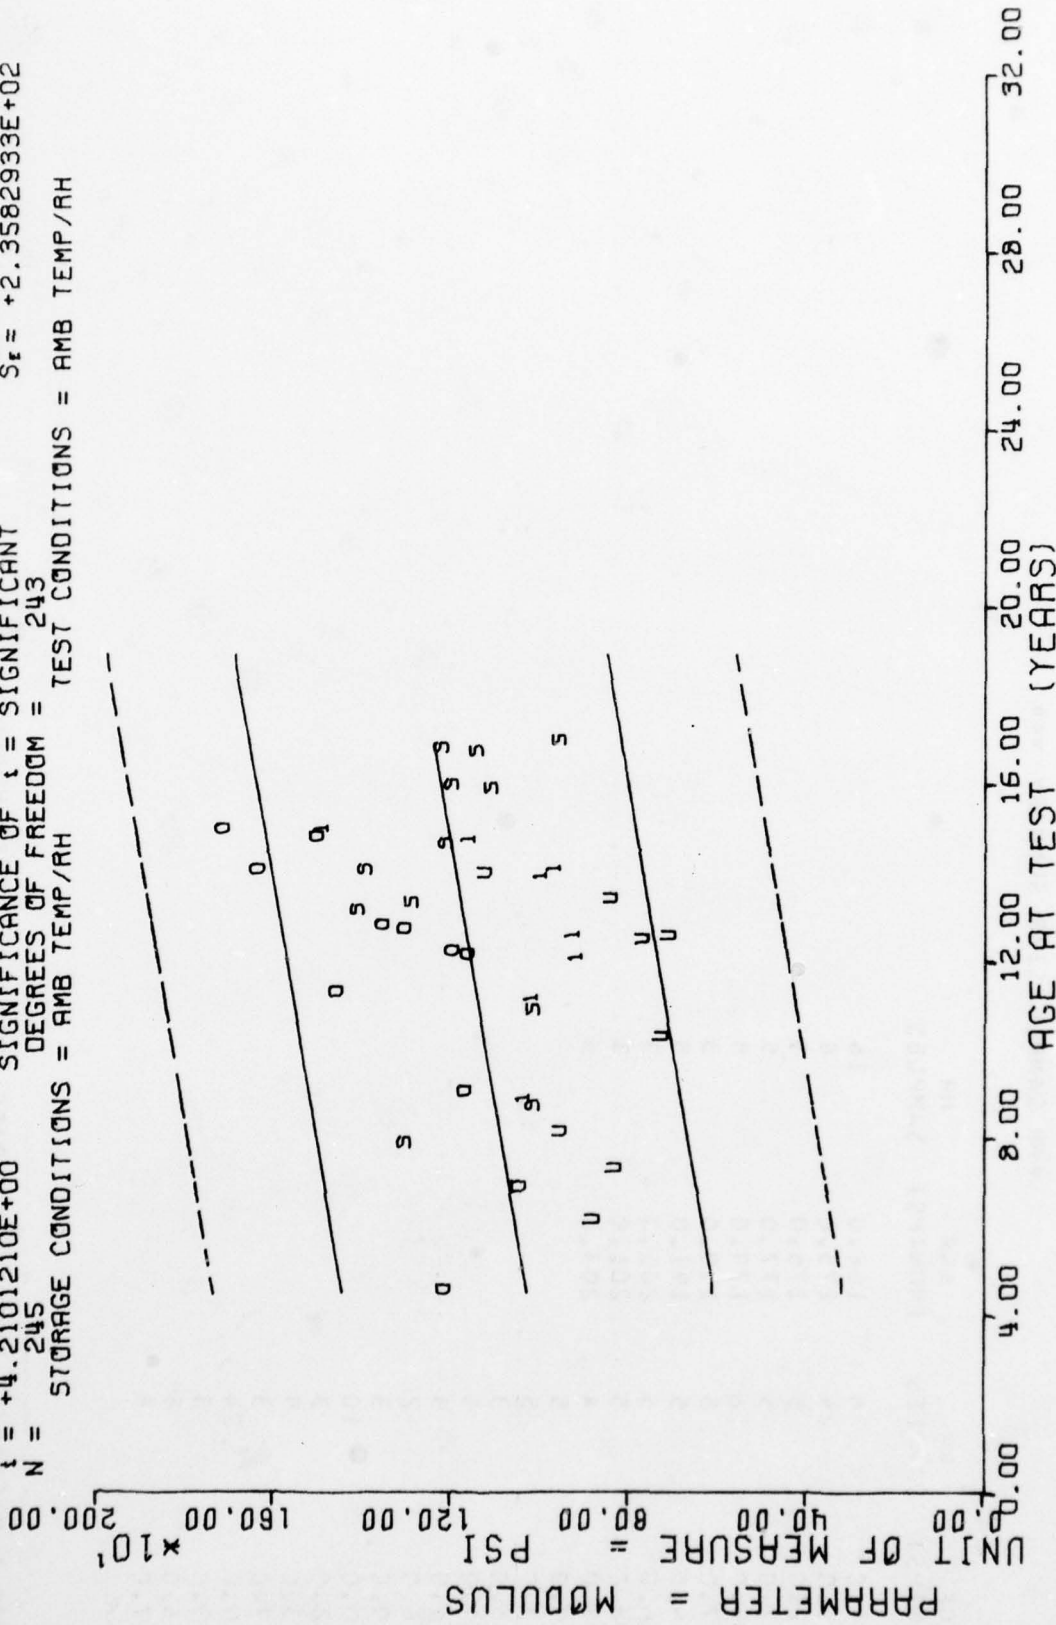

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=2.0 IN/MIN, MODULUS

Figure 5


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
82.0	2	177.0	2
97.0	5	179.0	8
104.0	2	190.0	3
106.0	5	191.0	5
108.0	5	200.0	3
116.0	5	201.0	3
118.0	5	203.0	5
123.0	5		
130.0	5		
133.0	14		
135.0	3		
140.0	5		
144.0	4		
145.0	3		
146.0	2		
150.0	9		
152.0	3		
153.0	5		
157.0	7		
160.0	5		
166.0	8		
167.0	7		
168.0	15		
175.0	8		
176.0	3		

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable to figures 6 thru 9.


$Y = ((+2.8859231E-01) + (-2.5283863E-04) * X)$
 F = +1.6555826E+01 SIGNIFICANCE OF F = SIGNIFICANT $\sigma_r = +2.3894996E-02$
 R = -3.0032490E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_n = +6.2139536E-05$
 t = +4.0688852E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_r = +2.2860068E-02$
 N = 169 DEGREES OF FREEDOM = 167
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

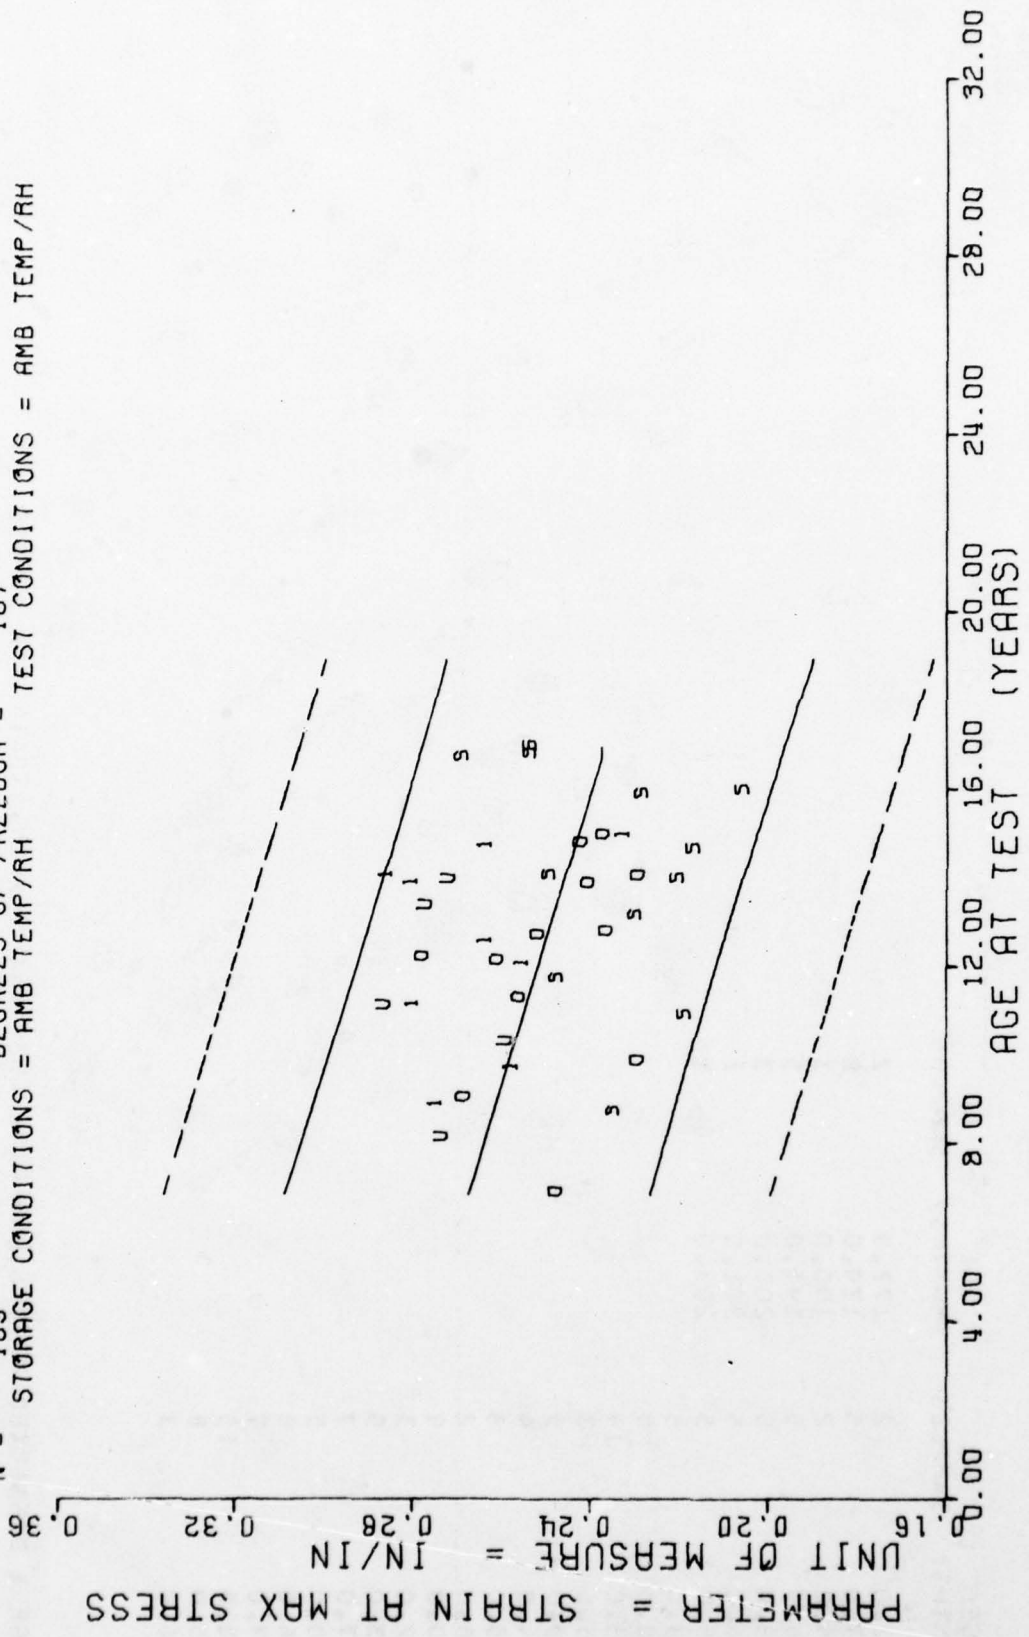

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN MAX STRESS

Figure 6


F = +4.5292311E-01
 R = -5.2007488E-02
 t = +6.7299563E-01
 N = 169
 STORAGE CONDITIONS = AMB TEMP/RH
 DEGREES OF FREEDOM = 167
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 Y = ((+1.5009684E+02) + (-2.4552180E-02) * X)
 S_y = +1.3399205E+01
 S_b = +3.6481931E-02
 S_e = +1.3421076E+01

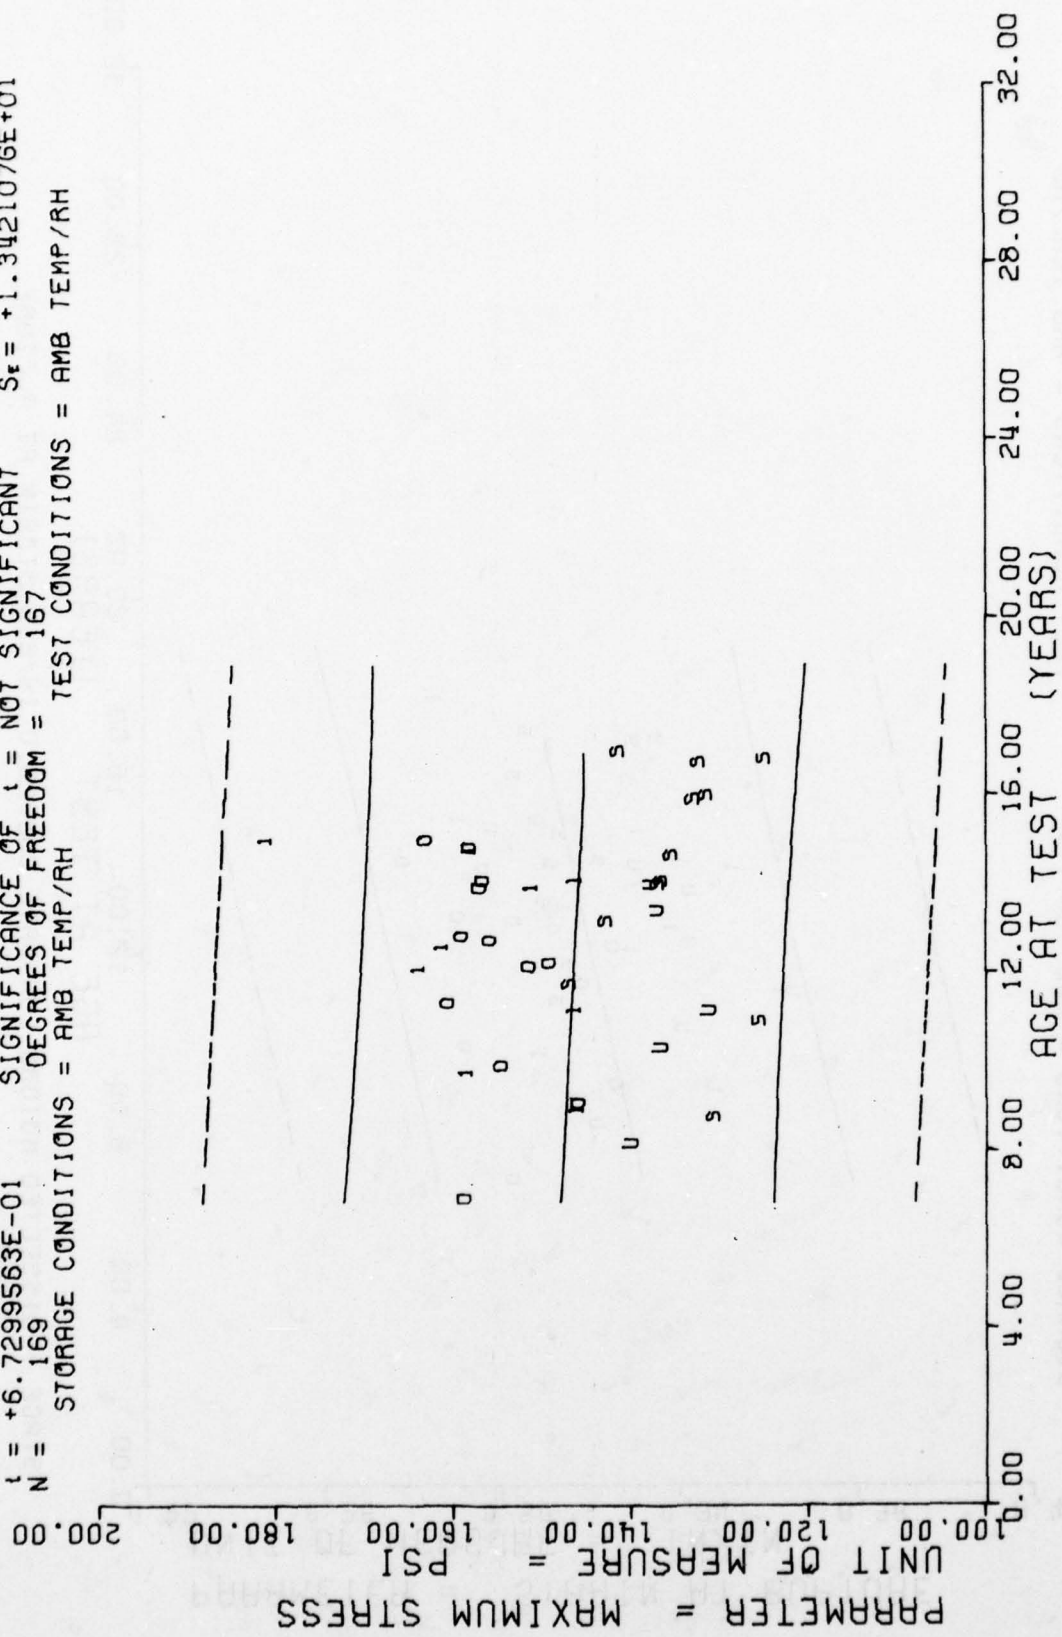

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MAXIMUM STRESS

Figure 7


$Y = ((+3.4808909E-01) + (-1.8621584E-04) * X)$
 F = +6.9922174E+00 SIGNIFICANCE OF F = SIGNIFICANT
 R = -2.0046684E-01 SIGNIFICANCE OF R = SIGNIFICANT
 t = +2.6442801E+00 SIGNIFICANCE OF t = SIGNIFICANT
 N = 169 DEGREES OF FREEDOM = 167
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

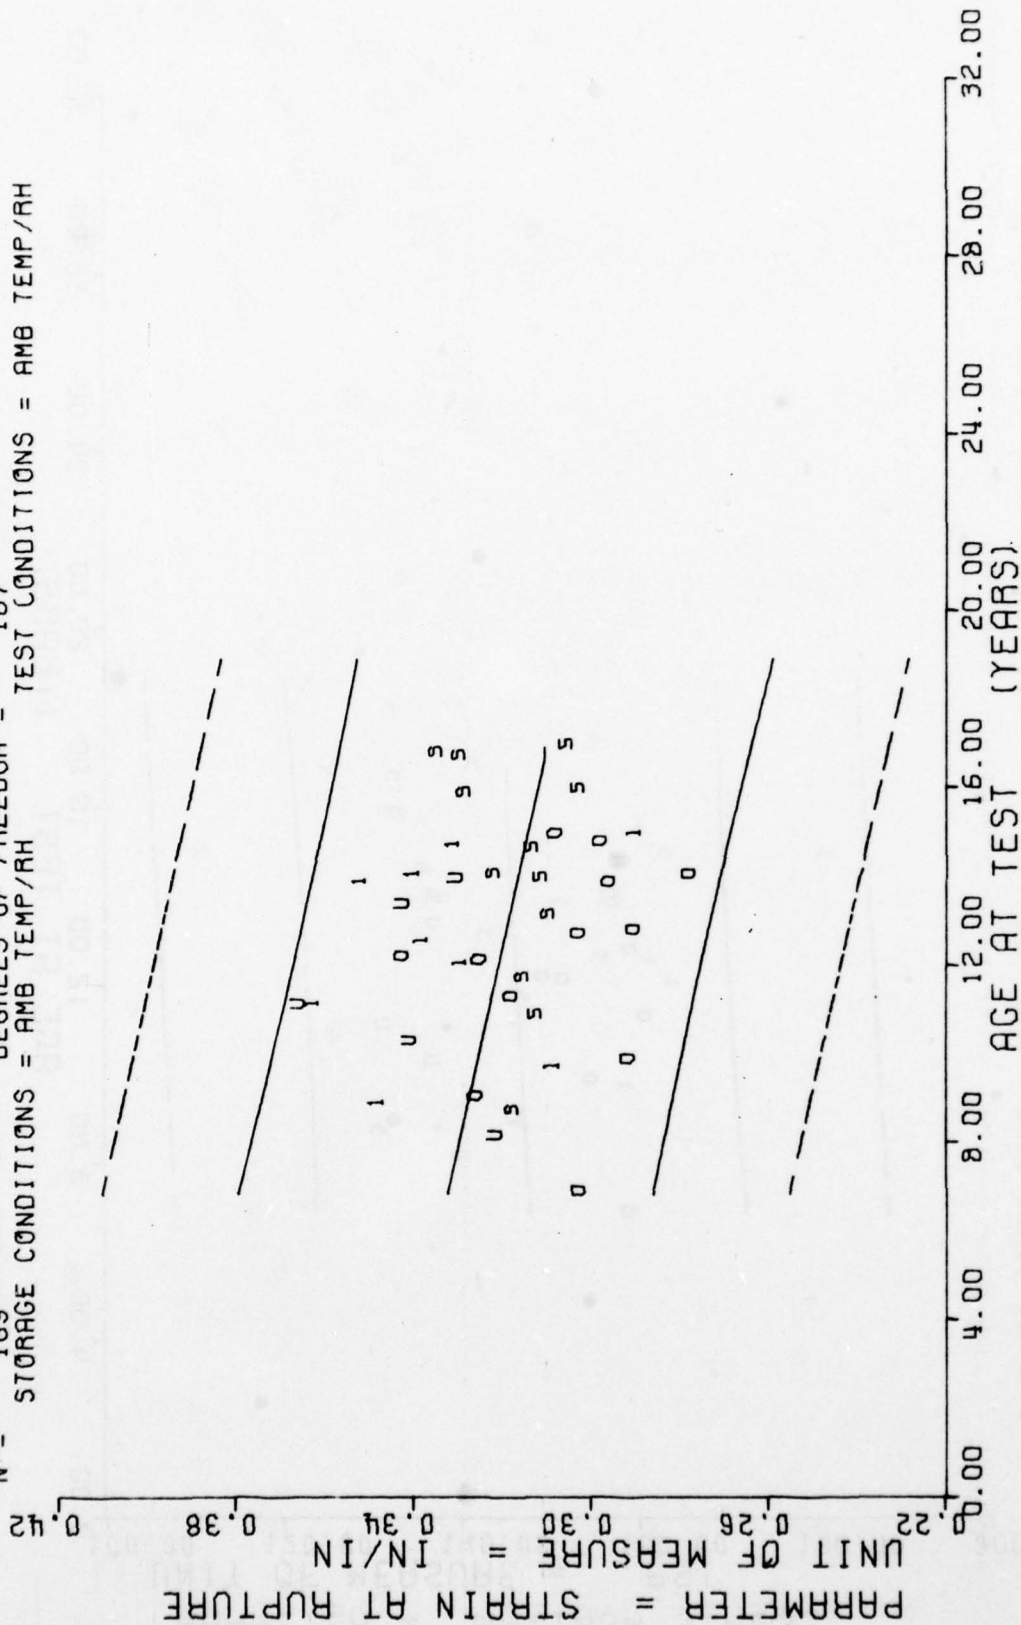

STAGE I DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRAIN AT RUPTURE

Figure 8

F = +4.0106320E+00 SIGNIFICANCE OF F = SIGNIFICANT * X) $\sigma_1 = +1.3679462E+01$
 R = -1.5314218E-01 SIGNIFICANCE OF R = SIGNIFICANT $\sigma_2 = +3.6855524E-02$
 I = +2.0026562E+00 SIGNIFICANCE OF I = SIGNIFICANT $\sigma_3 = +1.3558514E+01$
 N = 169 DEGREES OF FREEDOM = 167
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

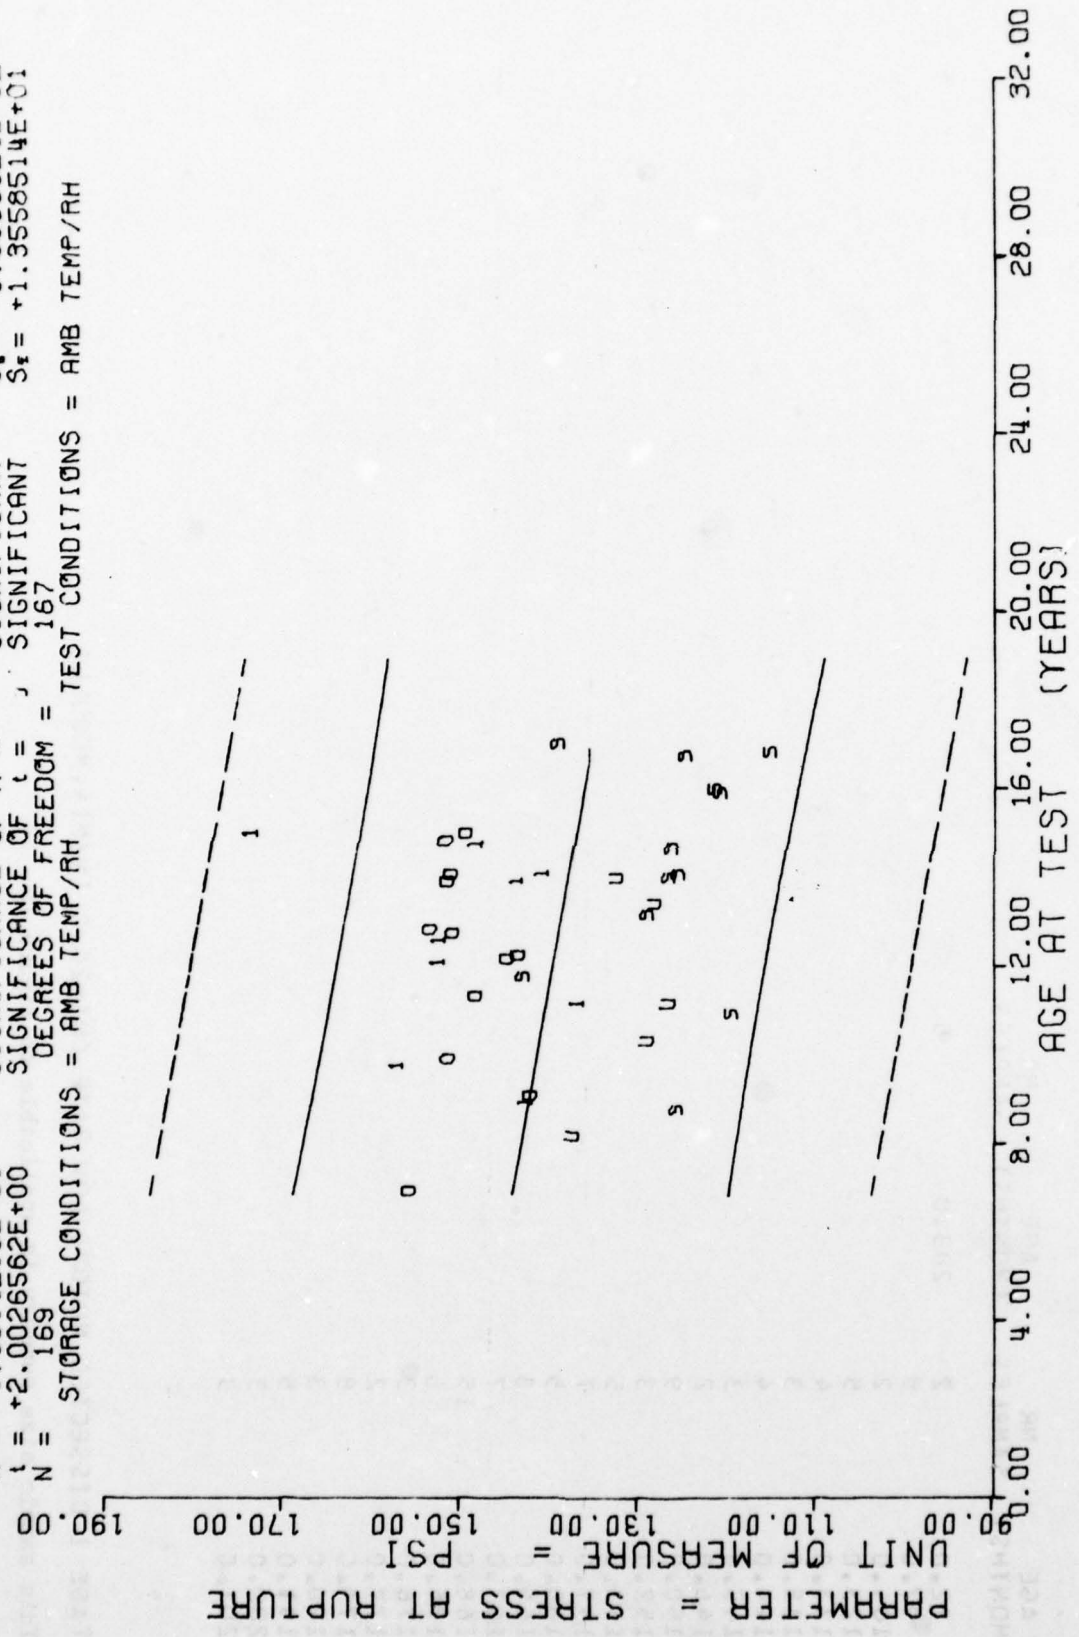

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, STRESS AT RUPTURE

Figure 9

*** SAMPLE SIZE SUMMARY ***


AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
82.0	2	203.0	5
97.0	5		
104.0	2		
123.0	5		
133.0	4		
135.0	3		
144.0	4		
145.0	3		
146.0	2		
150.0	9		
152.0	3		
153.0	5		
157.0	7		
160.0	5		
166.0	8		
167.0	7		
168.0	15		
175.0	8		
176.0	3		
177.0	2		
179.0	8		
190.0	3		
191.0	5		
200.0	3		
201.0	3		

1 24 1

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MCDULLS

This sample size summary is applicable to figure 10.

$Y = ((+1.9019340E+03) + (-1.2171520E+00) * X)$
 F = +7.0560118E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma = +4.2843670E+02$
 R = -7.4331804E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT $S = +1.4489893E+00$
 t = +8.4000070E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_f = +4.2893025E+02$
 N = 129 DEGREES OF FREEDOM = 127 TEST CONDITIONS = AMB TEMP / RH

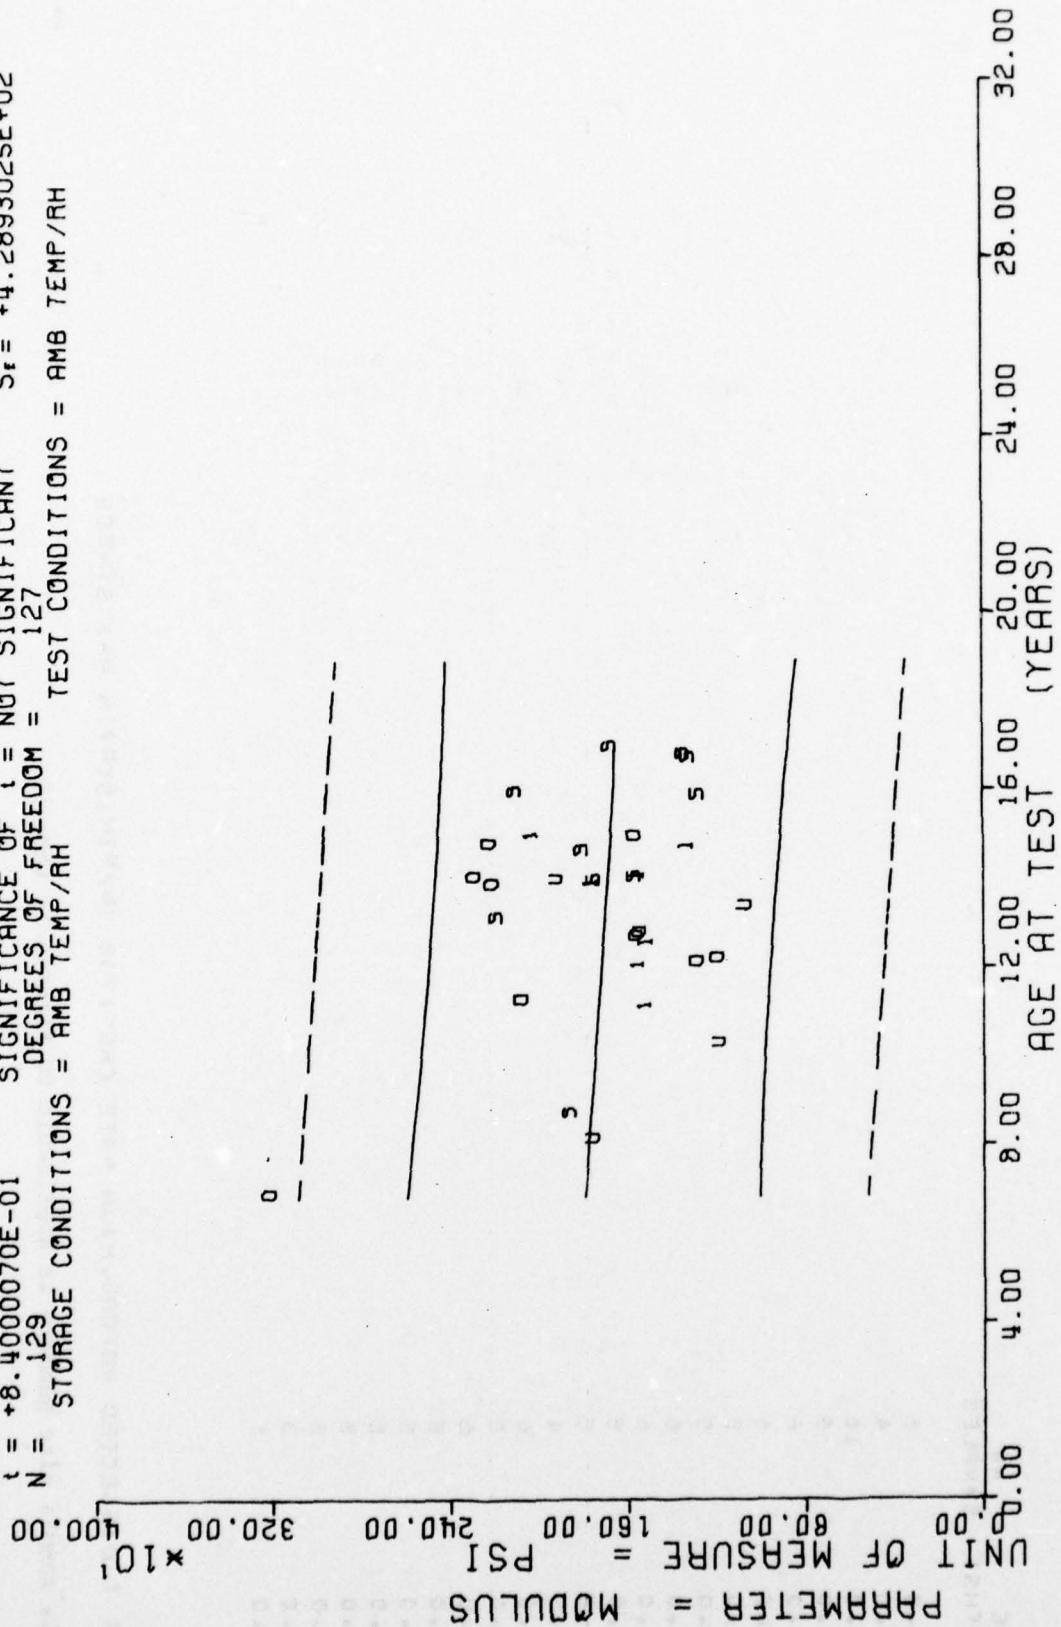

STAGE 1 DISSECTED MOTORS, LOW RATE CHS=20.0 IN/MIN, MODULUS

Figure 10

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
60.0	6
71.0	4
80.0	16
83.0	5
93.0	6
105.0	6
107.0	5
109.0	5
116.0	6
118.0	6
131.0	5
134.0	5
136.0	4
141.0	6
144.0	5
146.0	5
151.0	5
154.0	5
158.0	5
176.0	5
177.0	6
179.0	3
201.0	5

1 26 1


STAGE I DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRAIN MAX STRESS

This sample size summary is applicable to figures 11 thru 15.

F = +6.8833868E-01
 R = -7.3421875E-02
 t = +8.2966179E-01
 N = 129

Y = ((+2.0224644E-01) + (-1.0557065E-04) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 127


STORAGE CONDITIONS = AMB TEMP/AH
 TEST CONDITIONS = AMB TEMP/AH

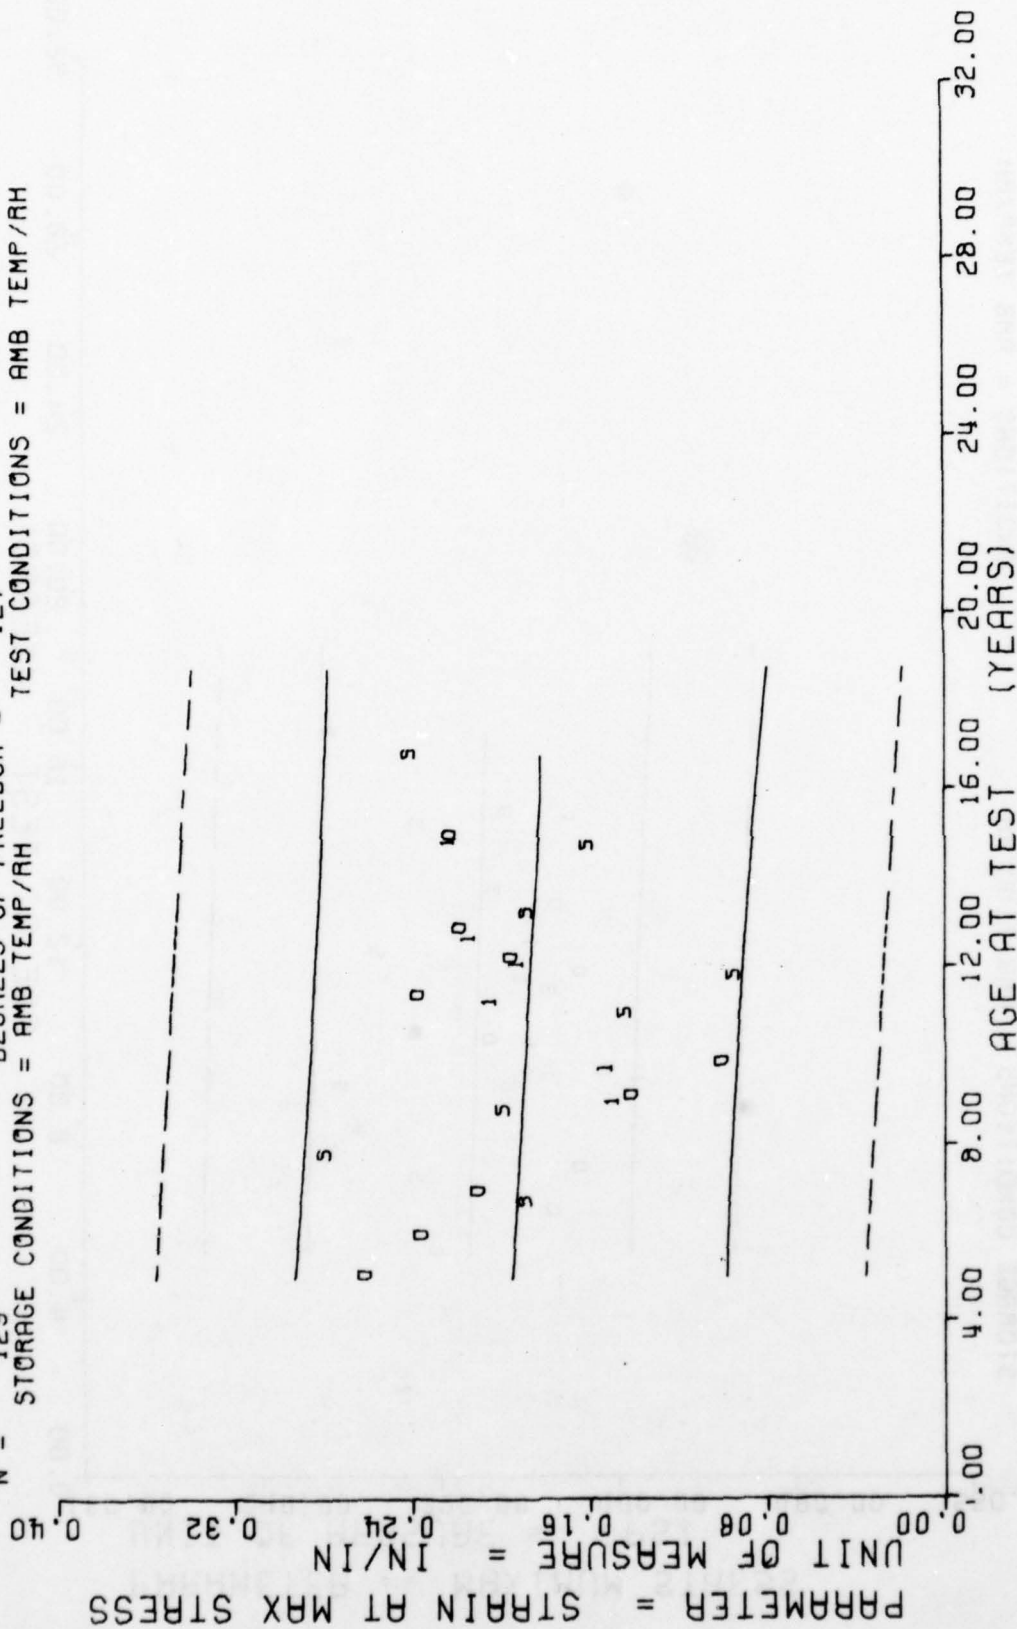

STAGE 1 DISSECTED MOTORS, HIGH RATE CMS=1750 IN/MIN, STRAIN MAX STRESS

Figure 11

Y = ((+3.2962349E+02) + (+5.4453789E-02) * X)
 F = +3.3059576E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT σ_1 = +3.9715888E+01
 R = +5.0954466E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT S_1 = +9.4706429E-02
 t = +5.7497457E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT S_2 = +3.9820149E+01
 N = 129 DEGREES OF FREEDOM = 127
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

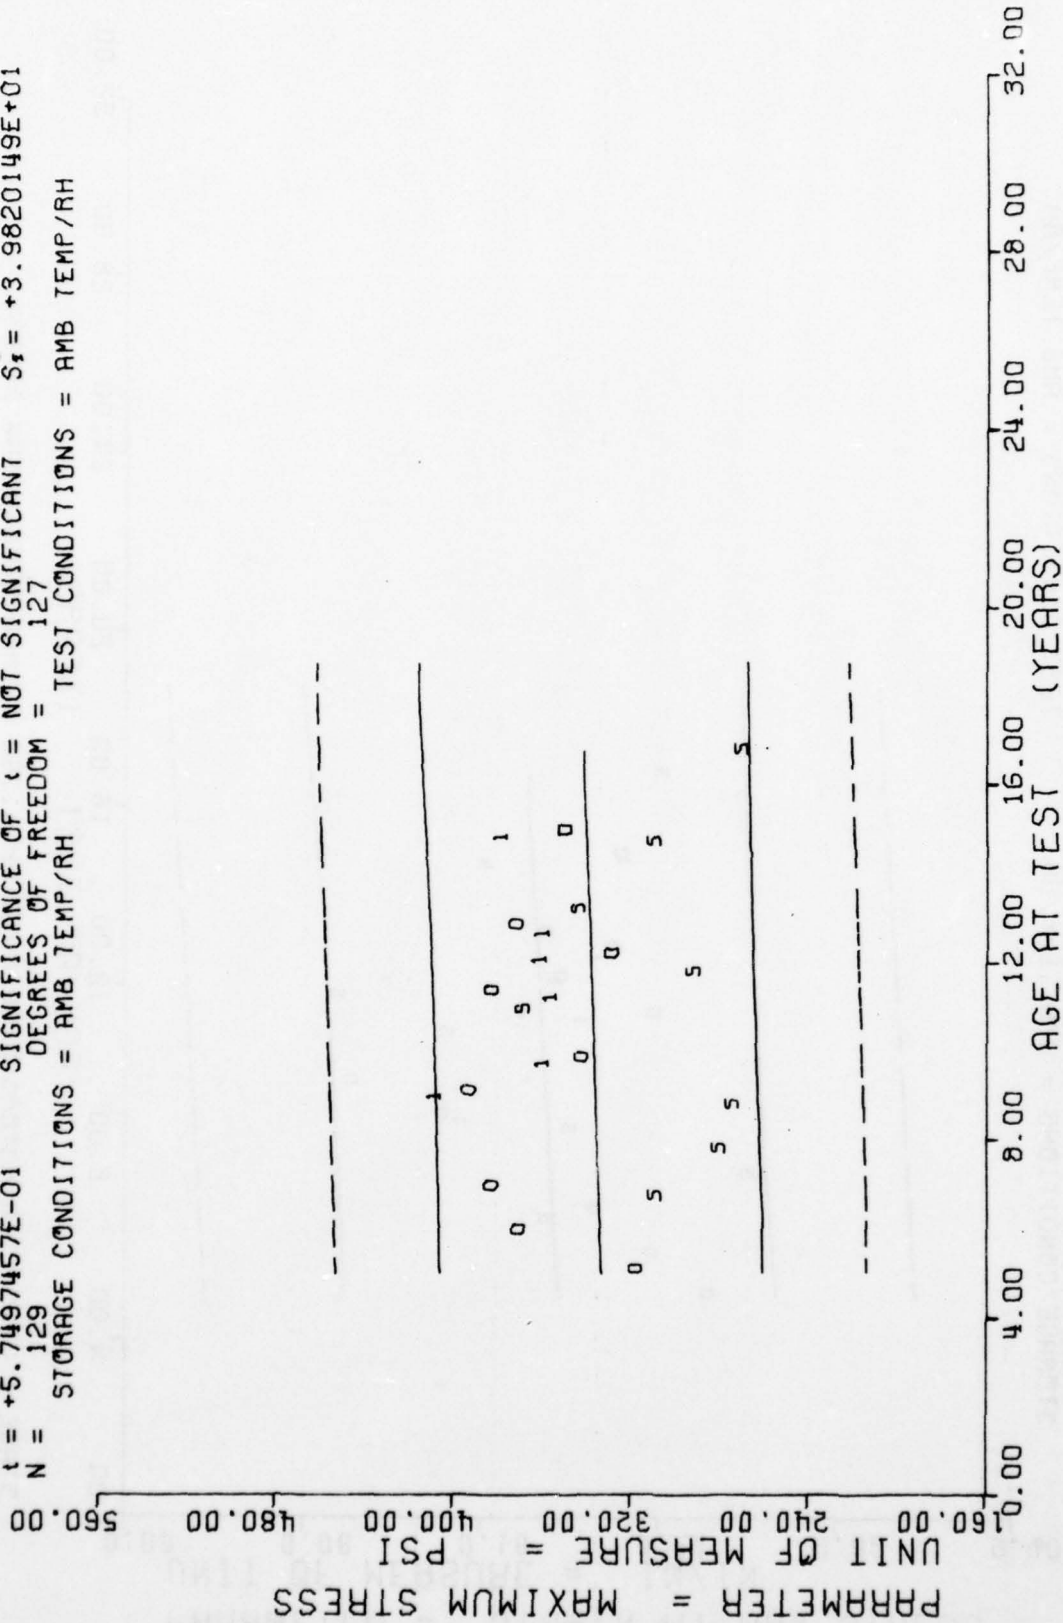


STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, MAXIMUM STRESS

Figure 12

F = +6.5792435E-01
 R = -7.1790023E-02
 I = +8.1112536E-01
 N = 129

Y = ((+3.4478699E-01) + (-5.6865247E-05) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF I = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 127


STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

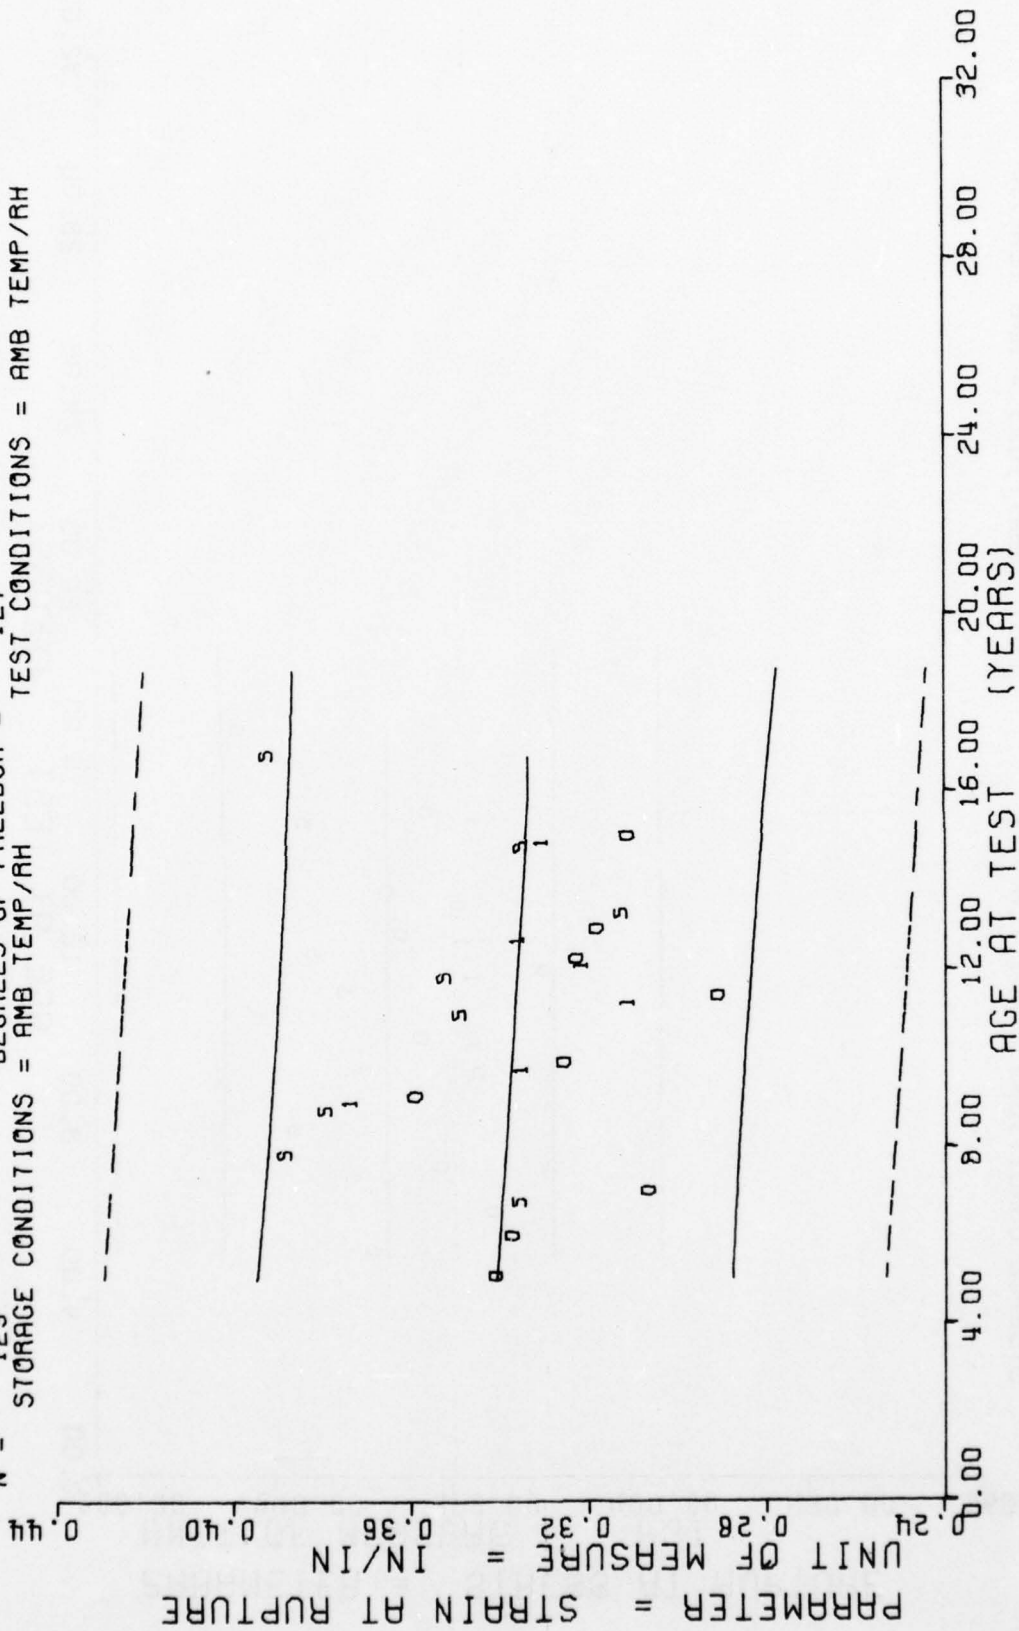

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRAIN AT RUPTURE

Figure 13


$Y = ((+2.9275595E+02) + (-1.0227717E-02) * X)$
 F = +1.0973285E-02 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_f = +4.0893044E+01$
 R = -9.2949643E-03 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_f = +9.7636091E-02$
 { = +1.0475345E-01 SIGNIFICANCE OF { = NOT SIGNIFICANT $S_f = +4.1051951E+01$
 N = 129 DEGREES OF FREEDOM = 127
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

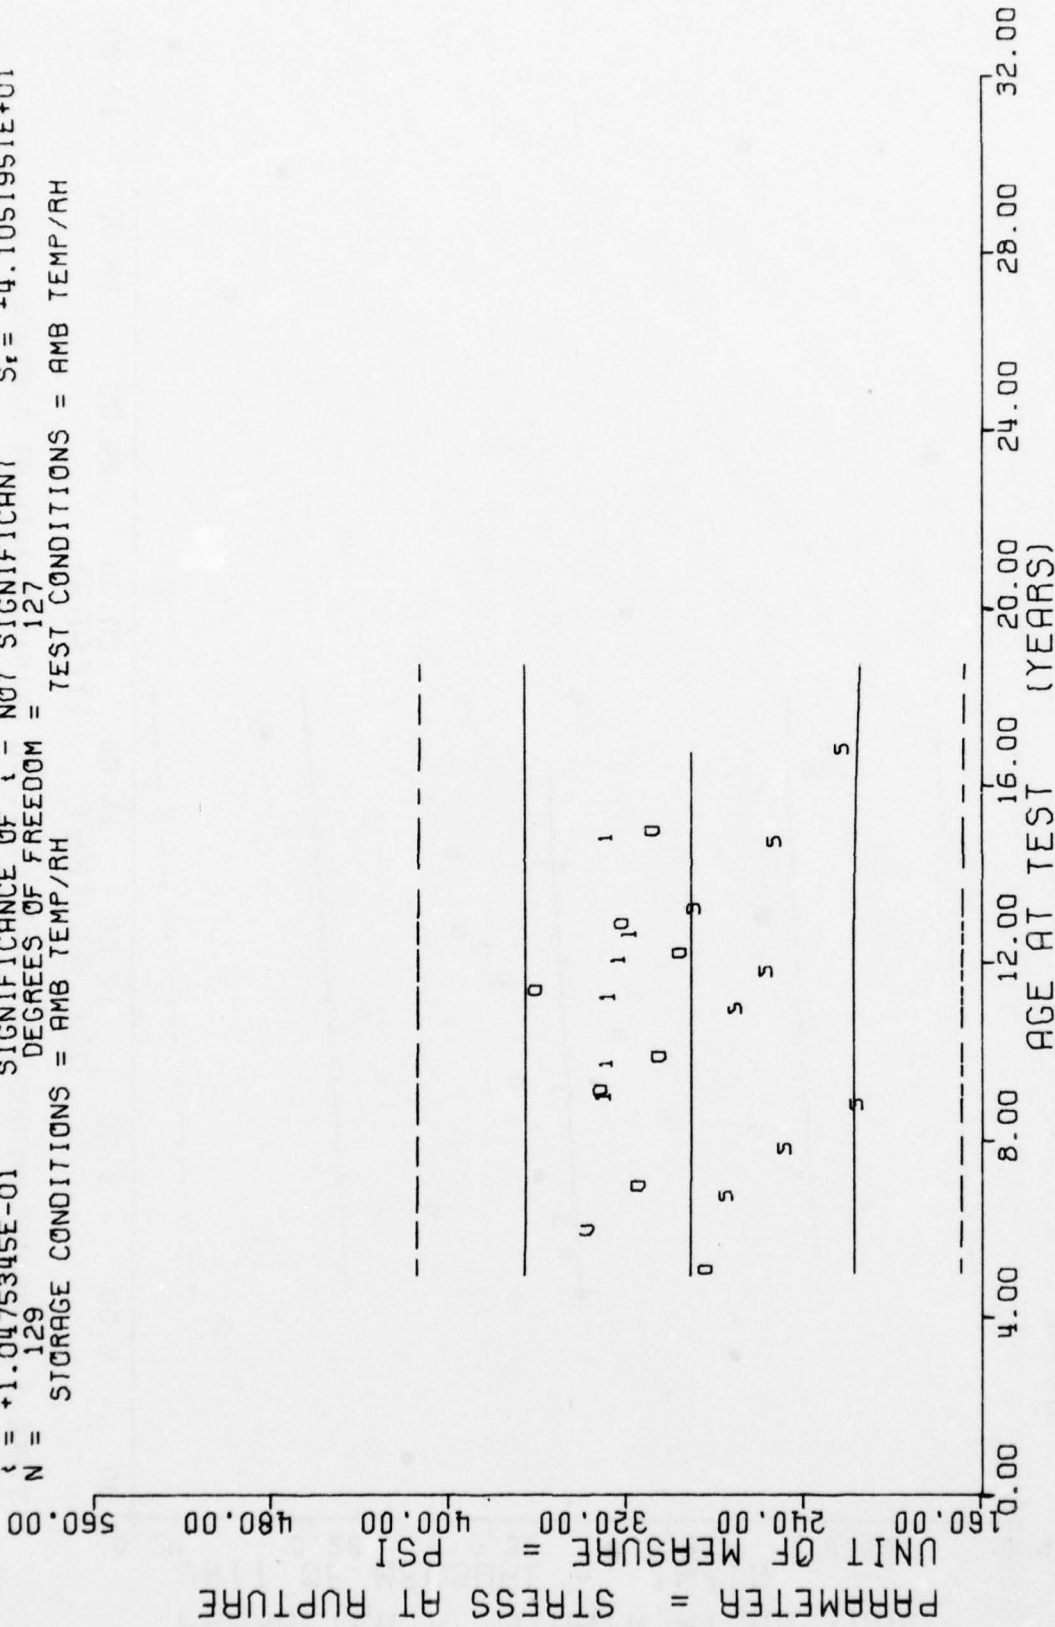

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, STRESS AT RUPTURE

Figure 14

$Y = ((+6.4384753E+03) + (+2.3003242E+00) * X)$
 F = +2.4369167E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_1 = +1.9534634E+03$
 R = +4.3762509E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_a = +4.6598154E+00$
 t = +4.9365136E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_r = +1.9592602E+03$
 N = 129 DEGREES OF FREEDOM = 127
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 9MB TEMP/RH

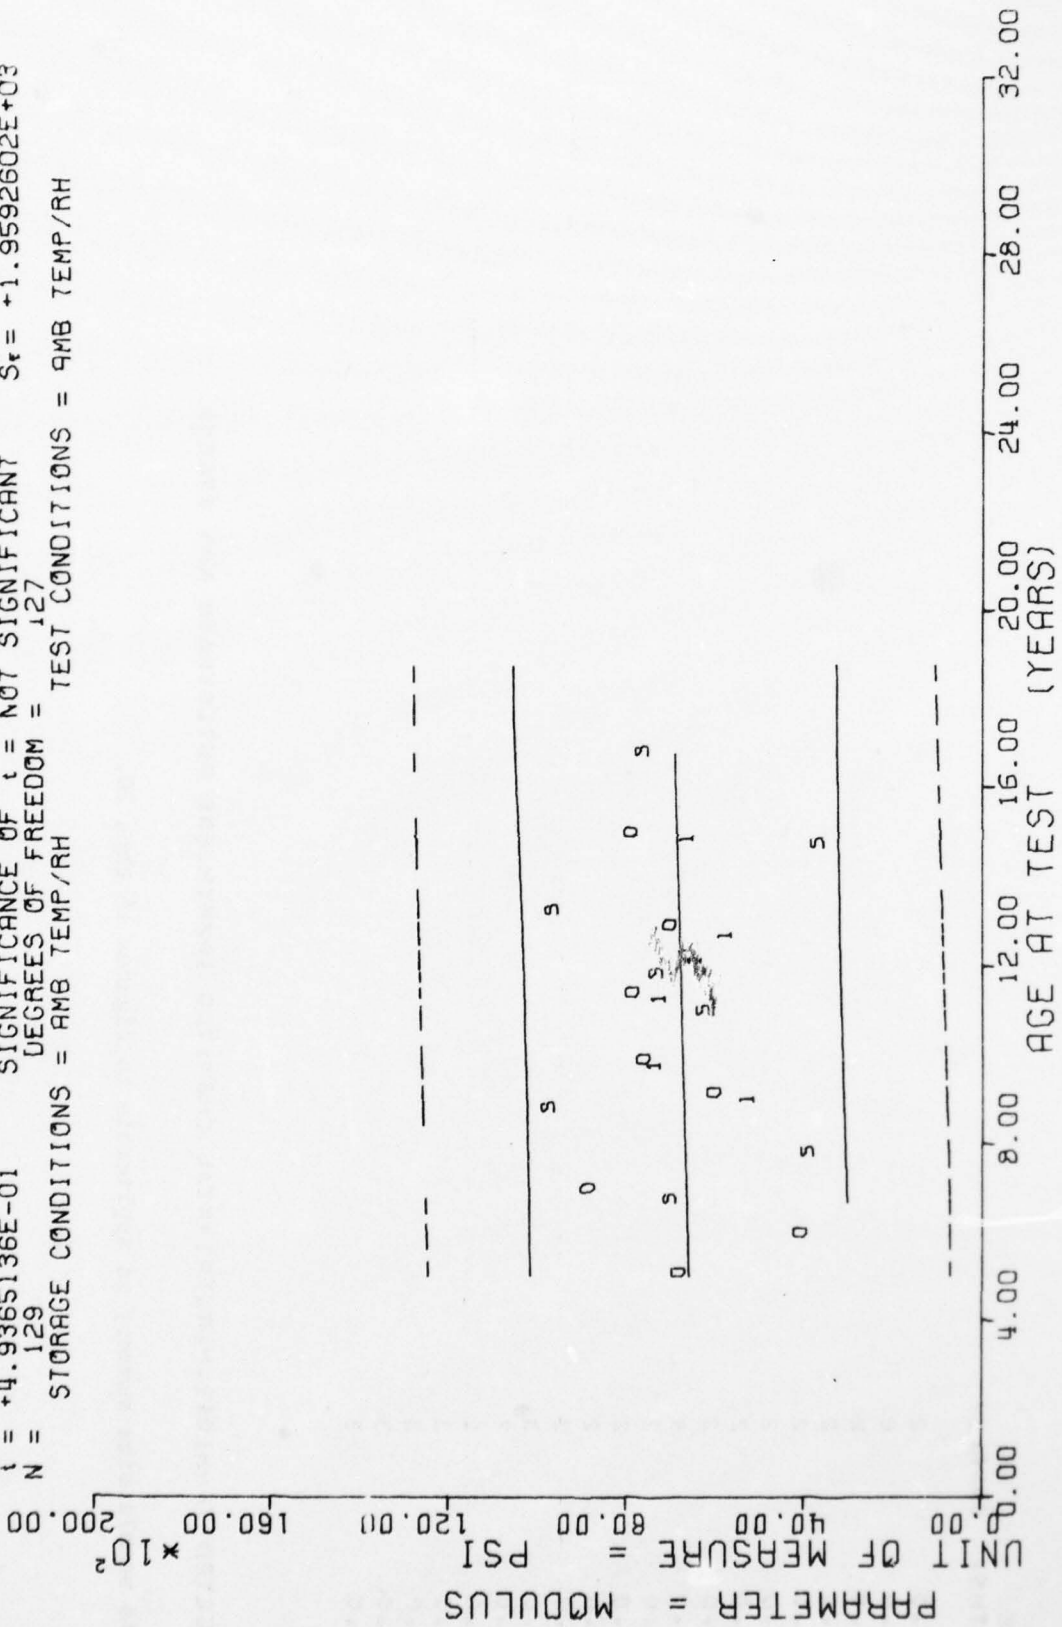

STAGE 1 DISSECTED MOTORS, HIGH RATE CHS=1750 IN/MIN, MODULUS

Figure 15


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NF SAMPLES
71.0	2
72.0	8
83.0	2
93.0	2
105.0	2
108.0	2
110.0	2
132.0	2
134.0	4
136.0	2
144.0	2
146.0	2
151.0	3
153.0	3
158.0	2
168.0	2
175.0	3
177.0	3
179.0	3
201.0	3

DISSECTED TP-H1011.H.R.TRIAXIAL CHS=1750 IN/MIN.600 PSI.STRAIN MAX STRESS

This sample size summary is applicable to figures 16 thru 20.

Y - ((+1.0678645E-01) + (+8.5248756E-04) * X)
 F = +8.5678671E+01 SIGNIFICANCE OF F = SIGNIFICANT S₁ = +4.3852012E-02
 R = +7.8886561E-01 SIGNIFICANCE OF R = SIGNIFICANT S₂ = +9.2098316E-05
 t = +9.2562774E+00 SIGNIFICANCE OF t = SIGNIFICANT S₃ = +2.7207844E-02
 N = 54 DEGREES OF FREEDOM = 52
 STORAGE CONDITIONS = 9MB TEMP/RH TEST CONDITIONS = 9MB TEMP/RH

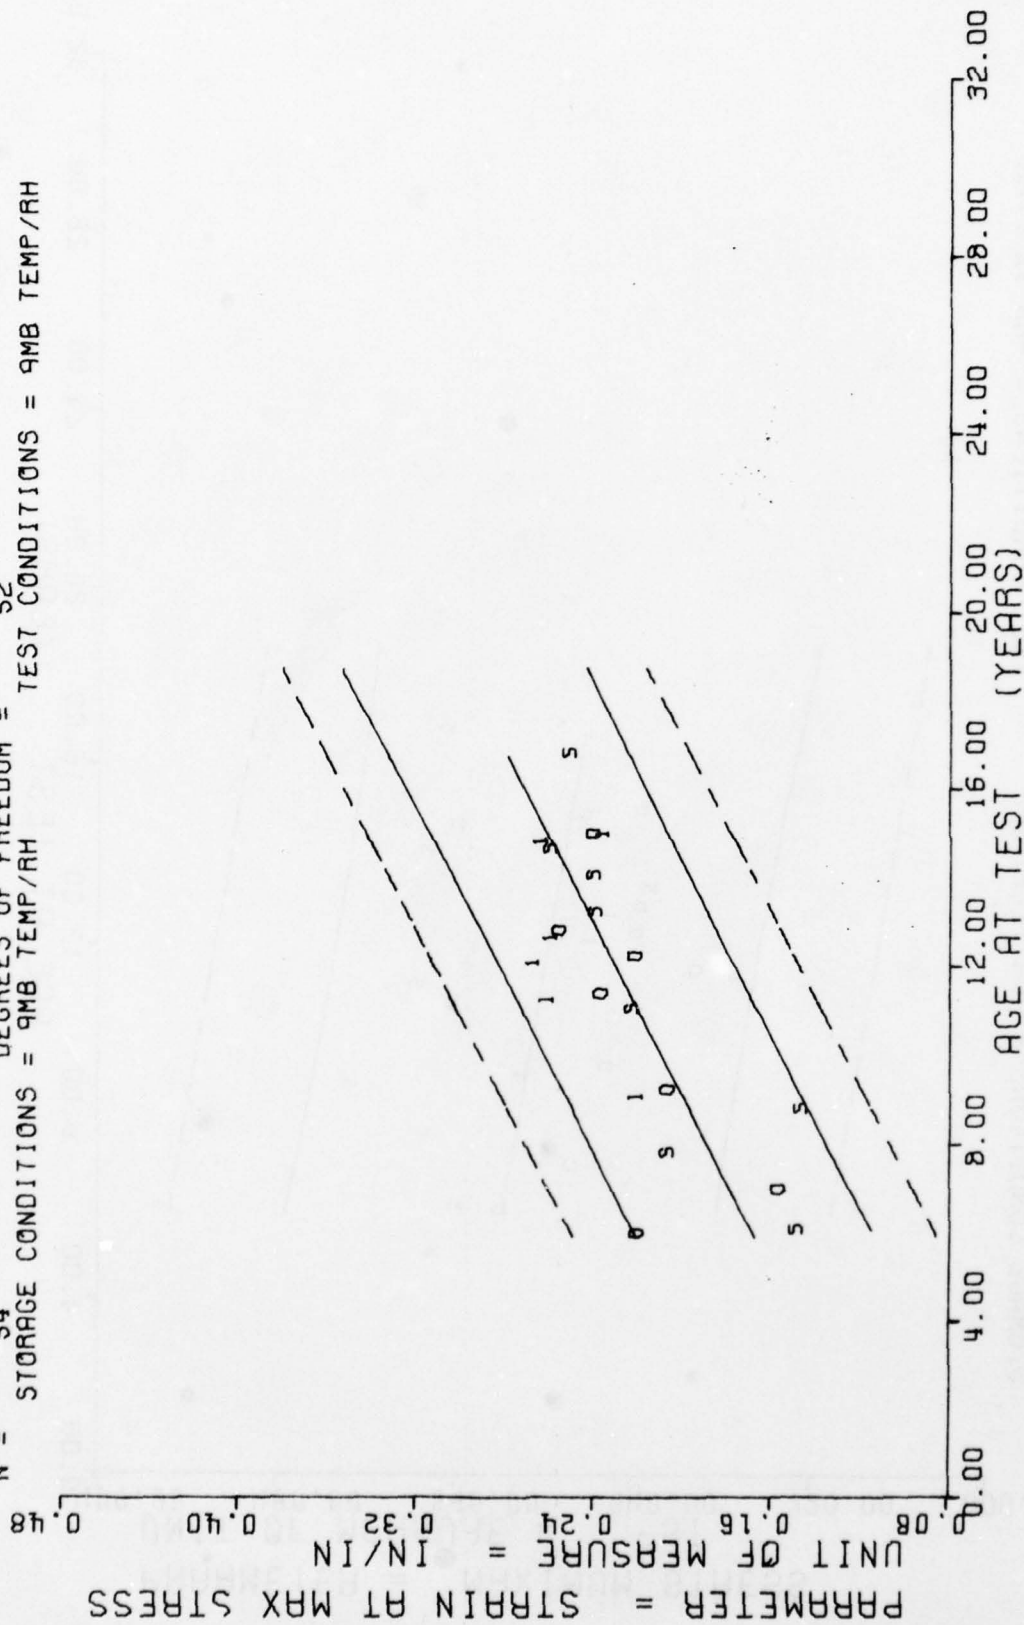


DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, STRAIN MAX STRESS

Figure 16

$Y = \{ +5.6136328E+02 \} + \{ +2.8536093E-01 \} * X$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 52
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 9MB TEMP/RH

F = +2.8719470E+00
 R = +2.2877735E-01
 t = +1.6946819E+00
 N = 54

G = +5.0615787E+01
 S = +1.6838612E-01
 S = +4.9744920E+01

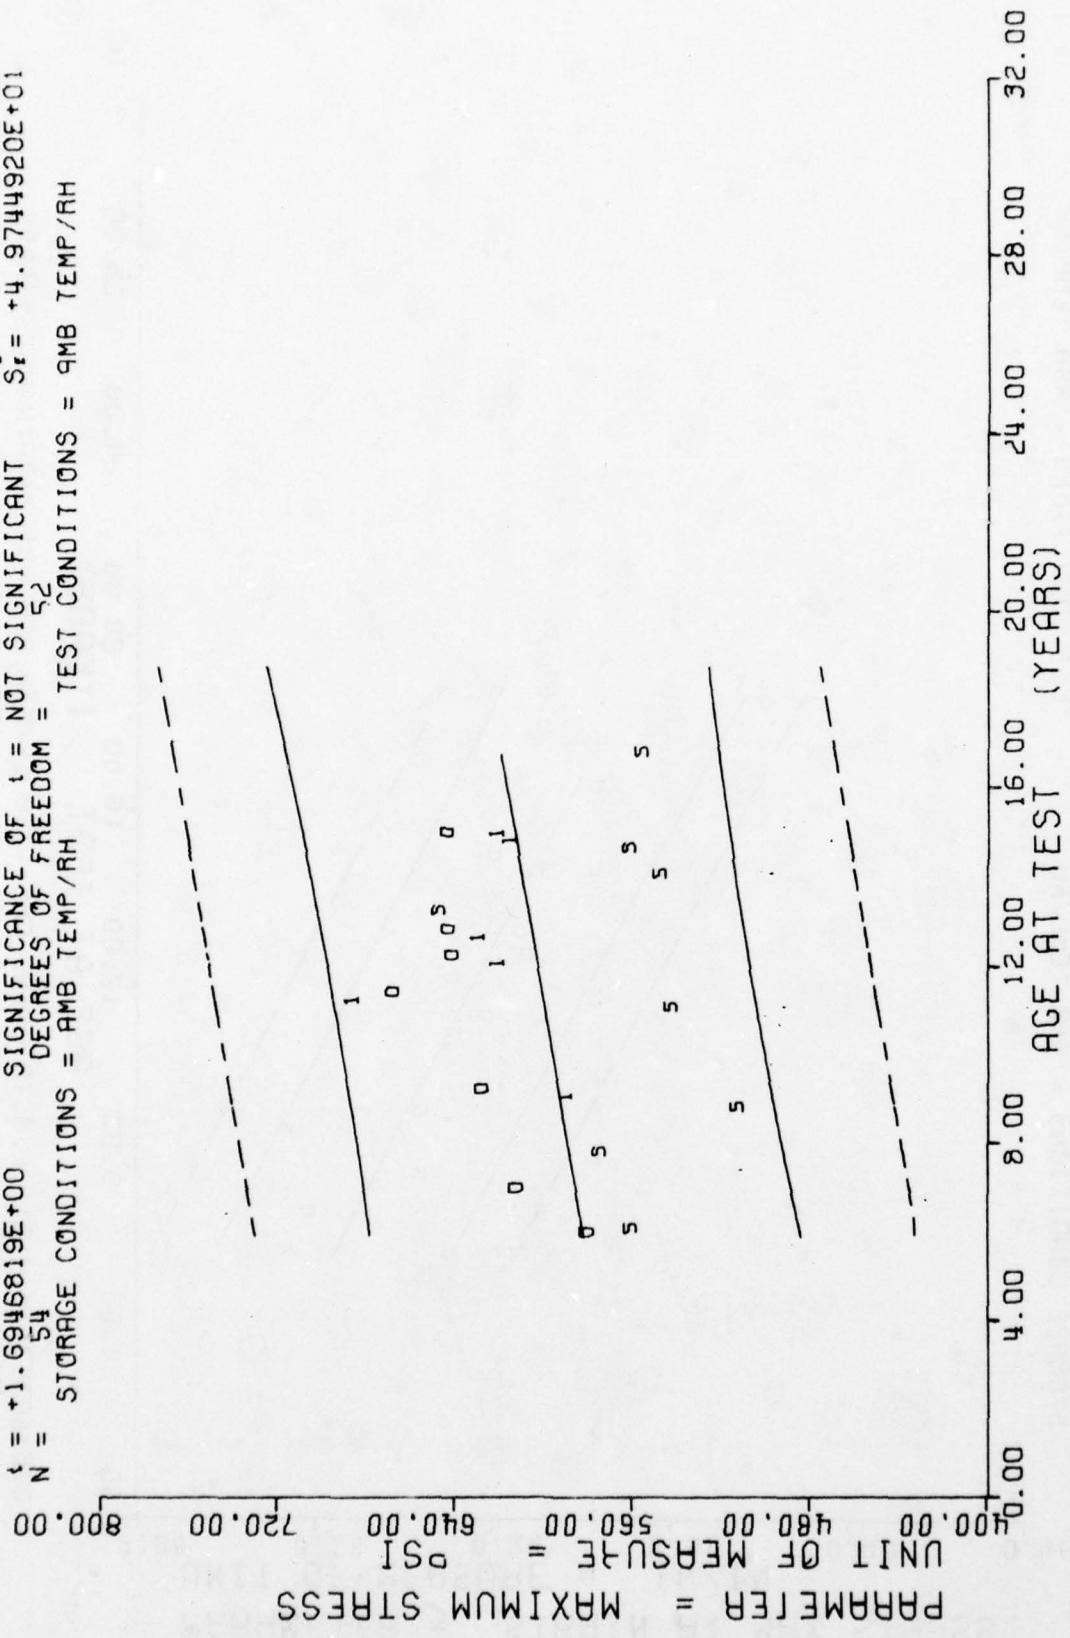


DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, MAXIMUM STRESS

Figure 17

$F = +3.9996396E+01$
 $R = +6.5936368E-01$
 $t = +6.3242704E+00$
 $N = 54$

$Y = ((+1.7998126E-01) + (+6.3570593E-04) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 52


STORAGE CONDITIONS = 9MB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

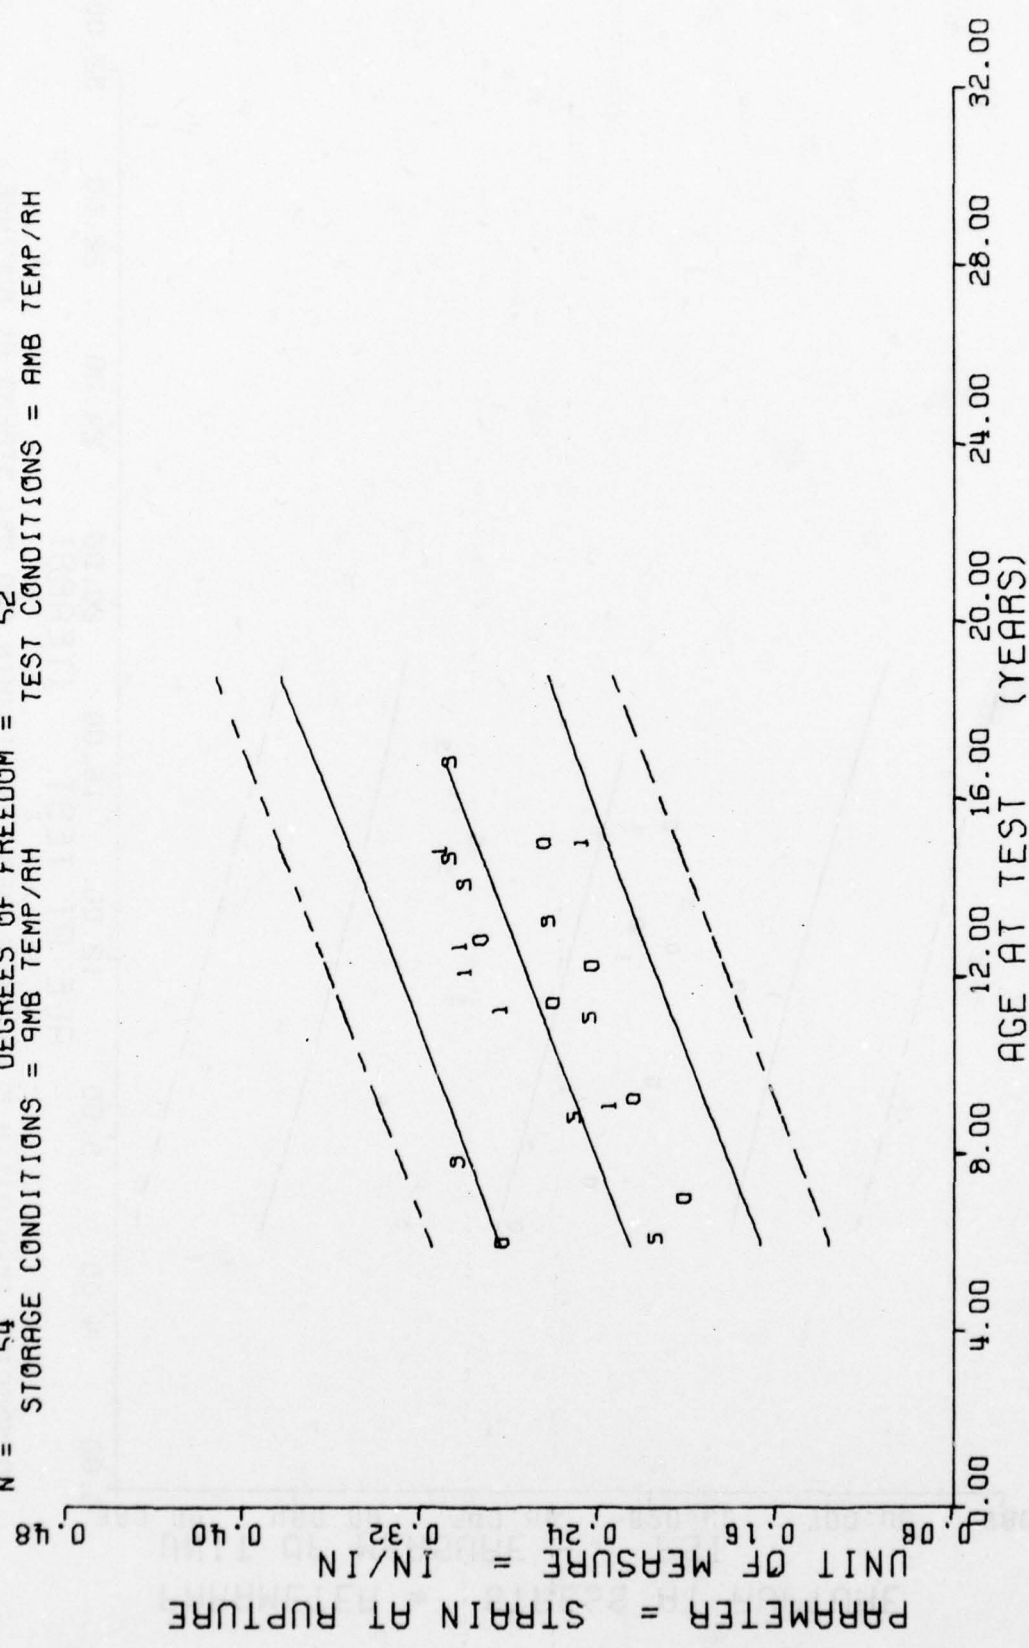

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, STRAIN AT RUPTURE

Figure 18

F = +5.5956776E+00
 R = +3.1169612E-01
 t = +2.3655184E+00
 N = 54
 STORAGE CONDITIONS = 9MB TEMP/RH
 Y - ((+5.2022907E+02) + (+4.3372470E-01) * X)
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 52
 TEST CONDITIONS = AMB TEMP/RH
 S_r = +5.6466032E+01
 S_s = +1.8335291E-01
 S_t = +5.4166435E+01

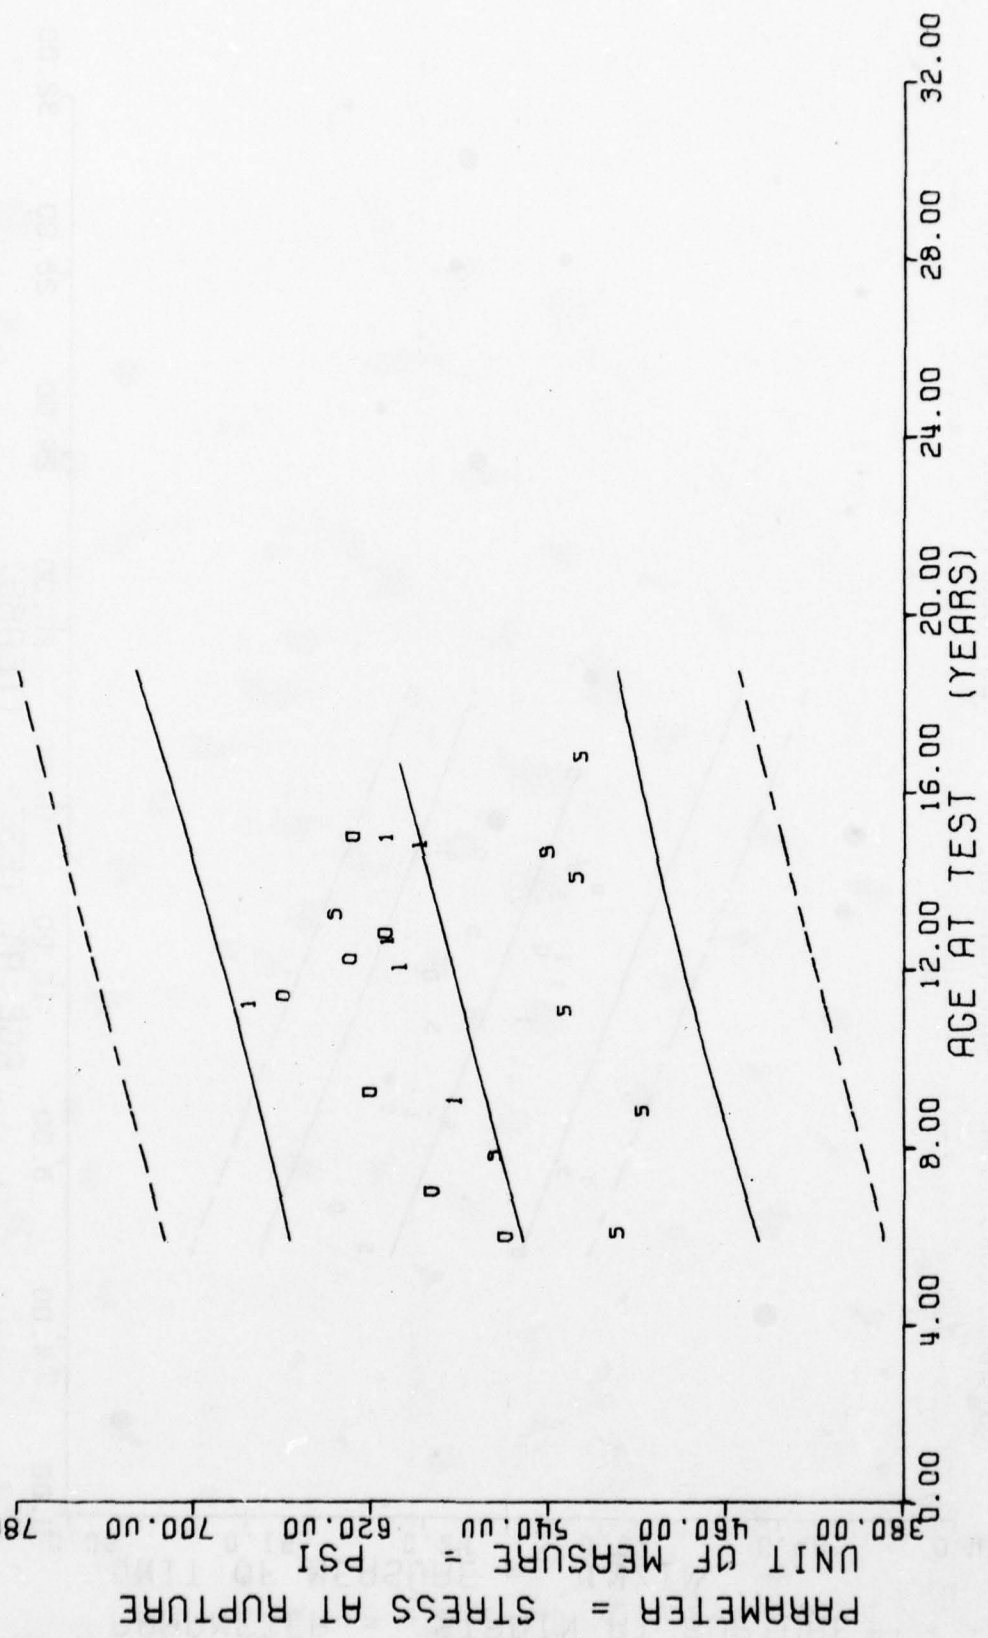

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, STRESS AT RUPTURE
 Figure 19


$F = +4.1538902E+01$
 $R = -6.6639445E-01$
 $t = +6.4450680E+00$
 $N = 54$

$Y = \{ (+9.7137868E+03) + (-2.7824564E+01) * X \}$

SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 52

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = 9MB TEMP/RH

$\sigma = +1.6943436E+03$
 $S_1 = +4.3171870E+00$
 $S_2 = +1.2753908E+03$

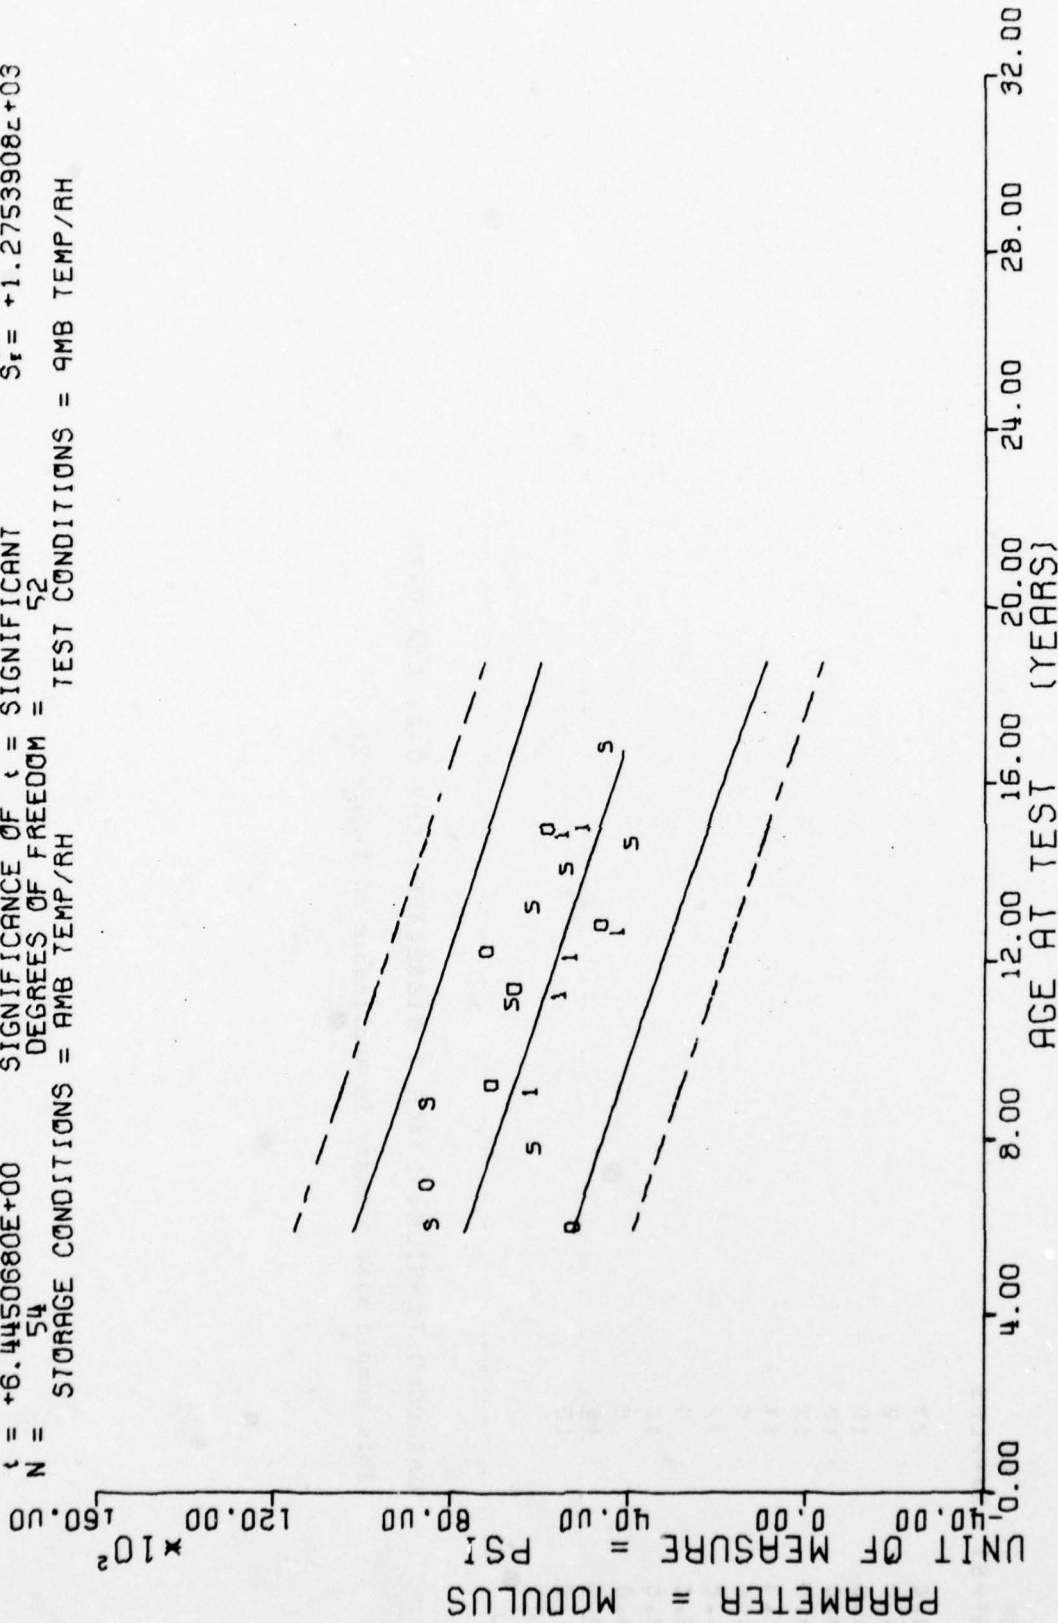

DISSECTED TP-H1011, H.R. TRIAXIAL CHS=1750 IN/MIN, 600 PSI, MODULUS

Figure 20

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
80.C	27
94.C	2
104.0	10
113.0	12
116.C	12
141.C	11
154.0	9
156.C	22
166.C	9
177.0	10
178.0	8
189.0	11
201.C	12

CASEEND TENSILE, STAGE 1 DISSECTED, CHS 0.2, CSA 0.75


This sample size summary is applicable to figure 21.

$F = +2.3099549E+01$
 $R = -3.6217847E-01$
 $t = +4.8061990E+00$
 $N = 155$

$Y = ((+1.2601173E+02) + (-1.8336740E-01) * X)$

SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 153

STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

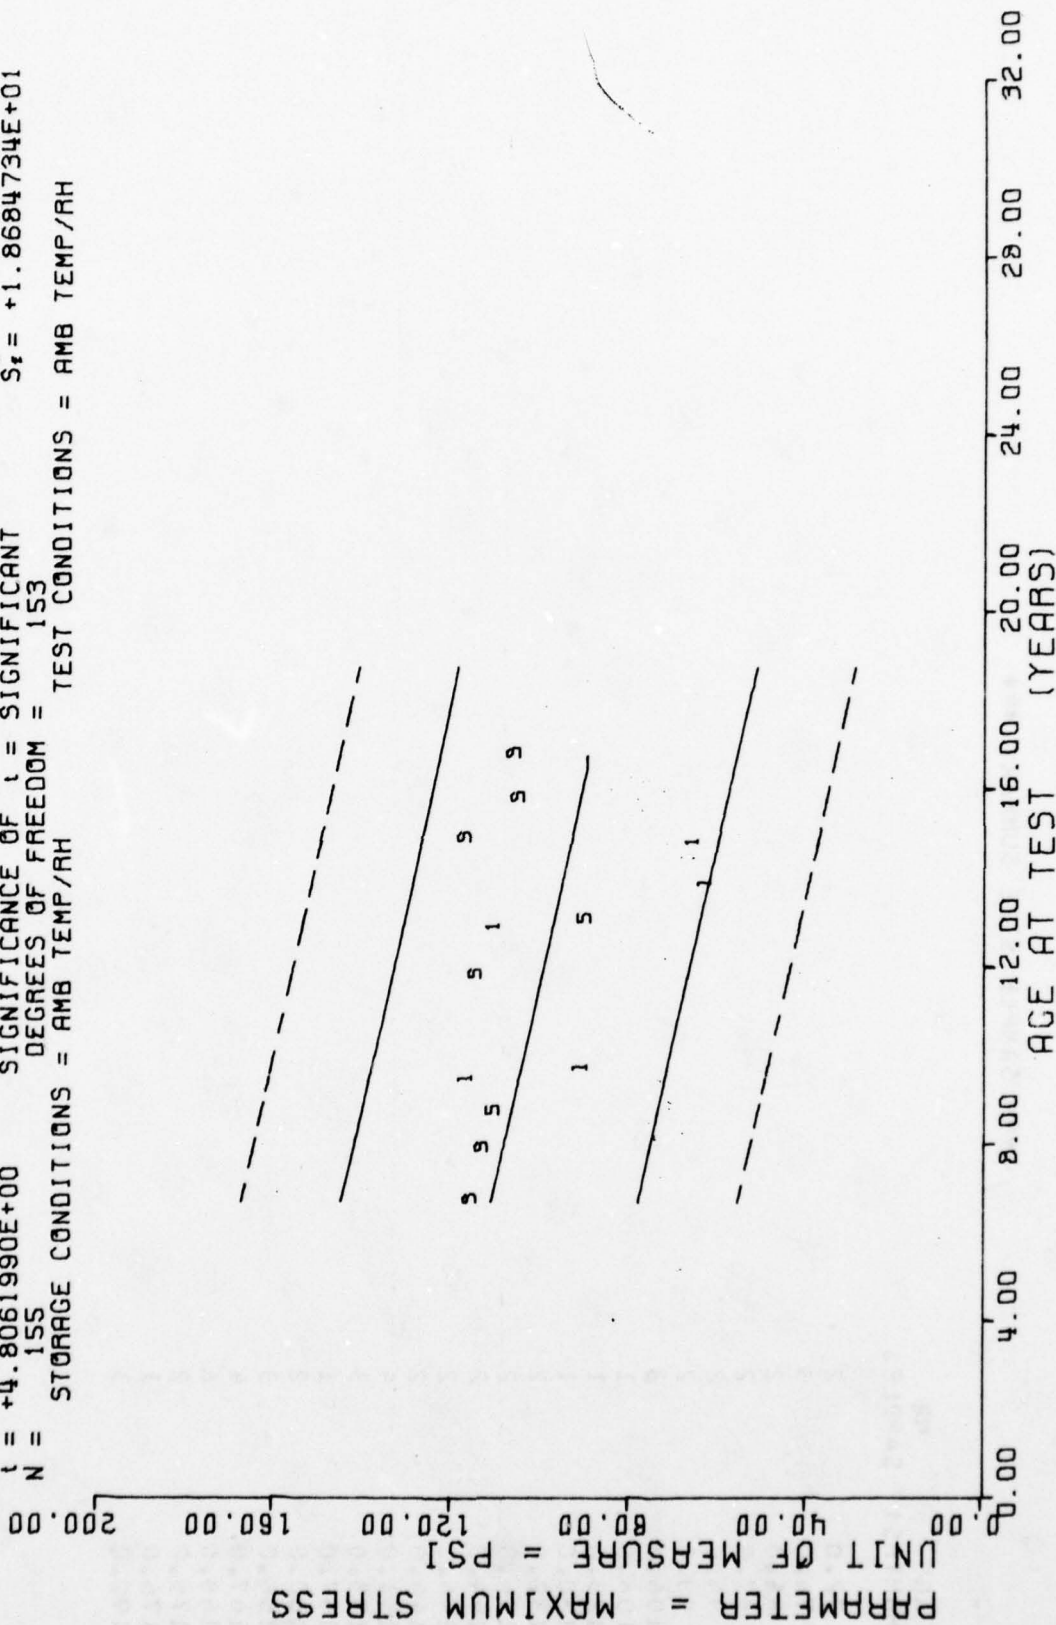

CASEBOND TENSILE, STAGE 1 DISSECTED, CHS 0.2, CSA 0.75

Figure 21


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
132.0	2
134.0	2
144.0	2
146.0	2
149.0	2
151.0	4
153.0	3
157.0	1
160.0	2
166.0	3
167.0	4
169.0	6
175.0	2
176.0	1
190.0	3

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10 SEC.

This sample size summary is applicable to figures 22 thru 24.


$Y = ((+1.4358396E-03) + (-2.5076507E-06) * X)$
 F = +5.2549770E+00 SIGNIFICANCE OF F = SIGNIFICANT
 R = -2.9289686E-01 SIGNIFICANCE OF R = SIGNIFICANT
 t = +2.2923736E+00 SIGNIFICANCE OF t = SIGNIFICANT
 N = 58 DEGREES OF FREEDOM = 56
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

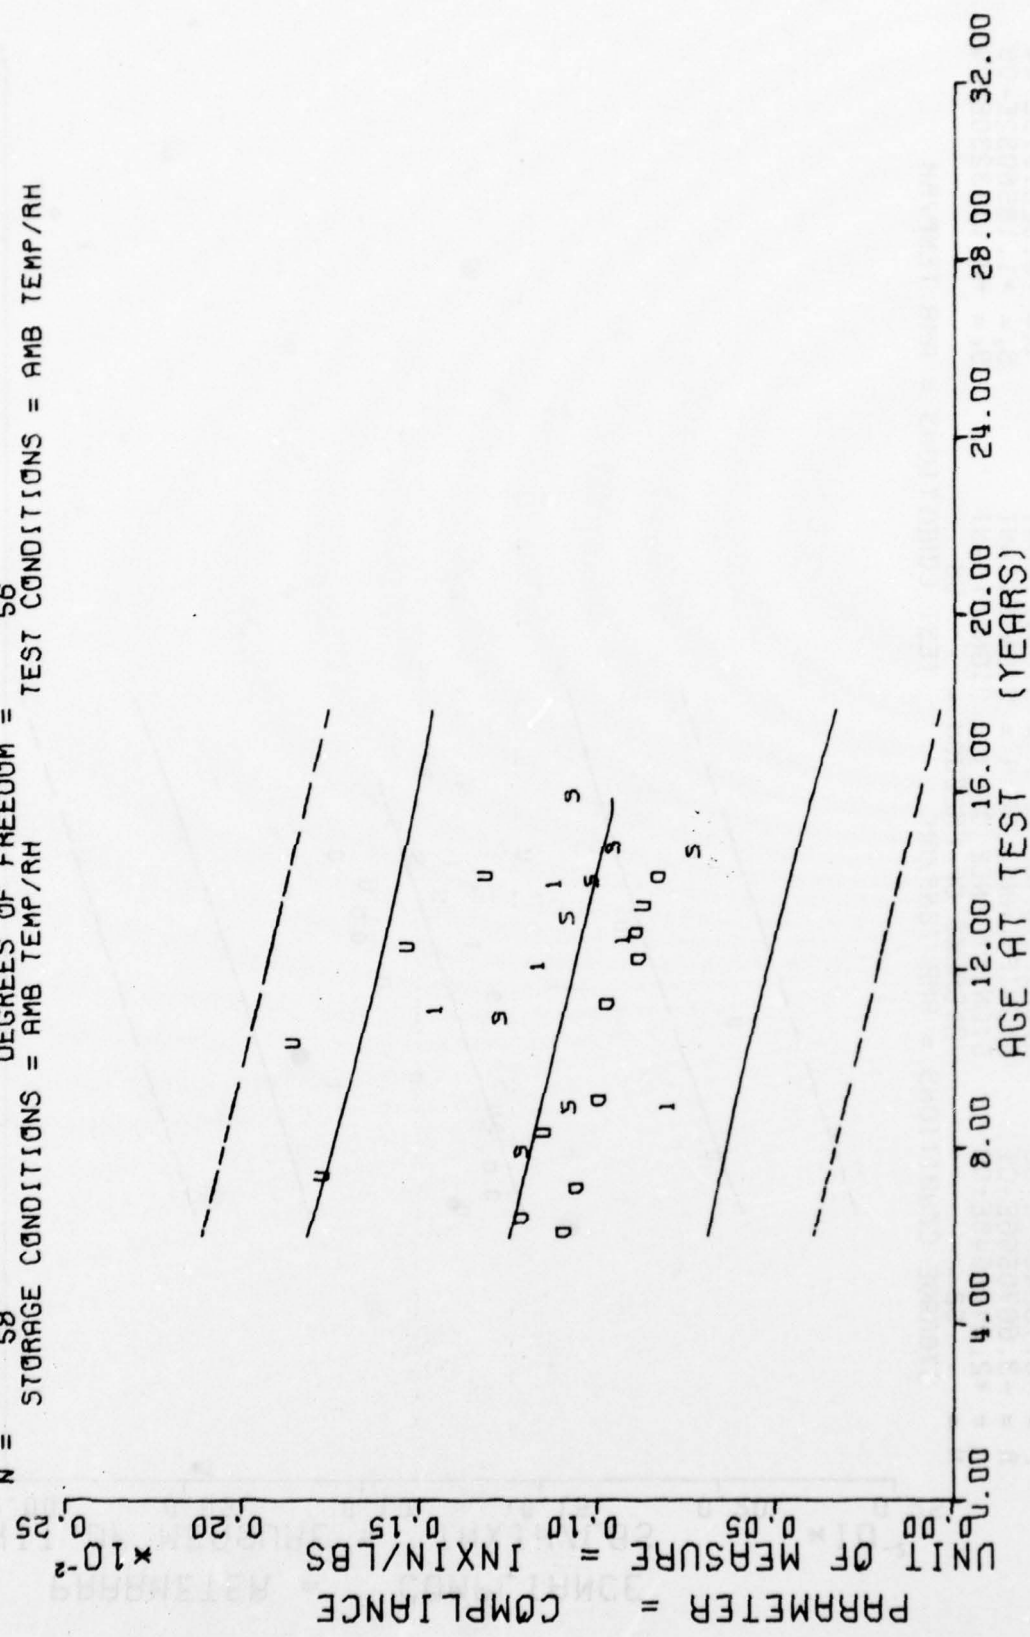

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10 SEC.

Figure 22


$Y = ((+1.7160942E-03) + (-3.4971202E-06) * X)$
 F = +8.7004637E+00 SIGNIFICANCE OF F = SIGNIFICANT
 R = -3.6670556E-01 SIGNIFICANCE OF R = SIGNIFICANT
 I = +2.9496548E+00 SIGNIFICANCE OF I = SIGNIFICANT
 N = 58 DEGREES OF FREEDOM = 56
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

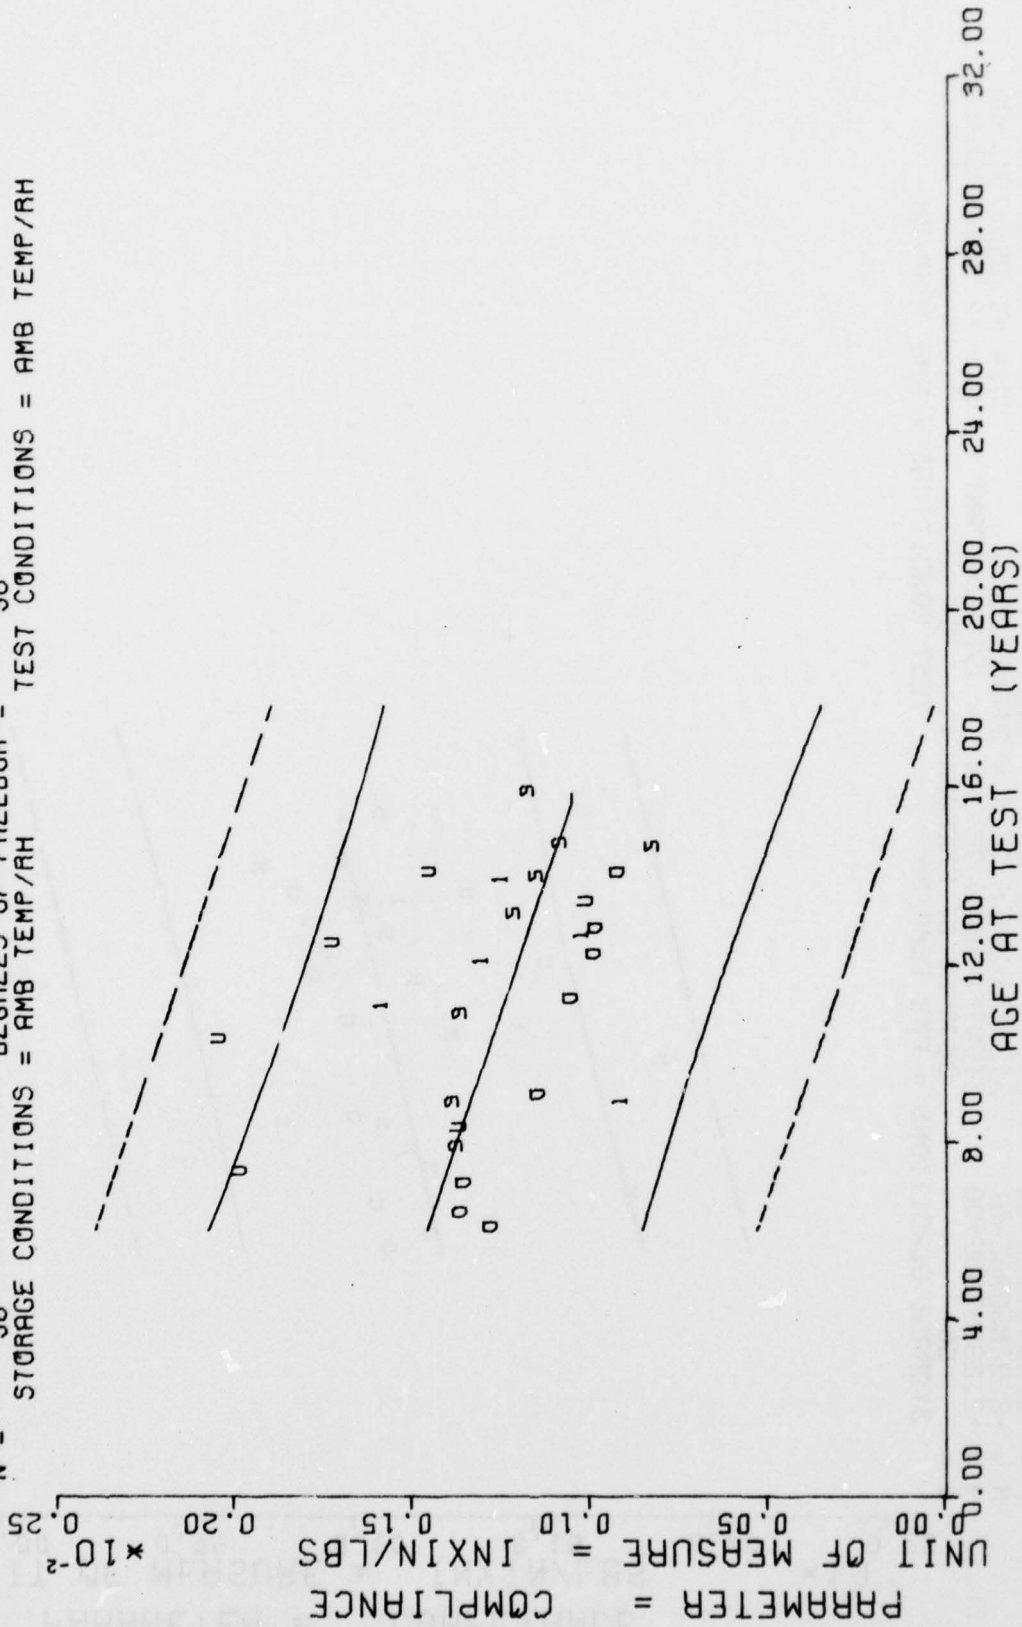

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 20 SEC.

Figure 23

$Y = ((+2.3591670E-03) + (-3.0793456E-06) * X)$
 F = +2.7021144E+00 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_f = +4.9968822E-04$
 R = -2.1454826E-01 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_f = +1.8732967E-06$
 t = +1.6438109E+00 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_t = +4.9239050E-04$
 N = 58 DEGREES OF FREEDOM = 56
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

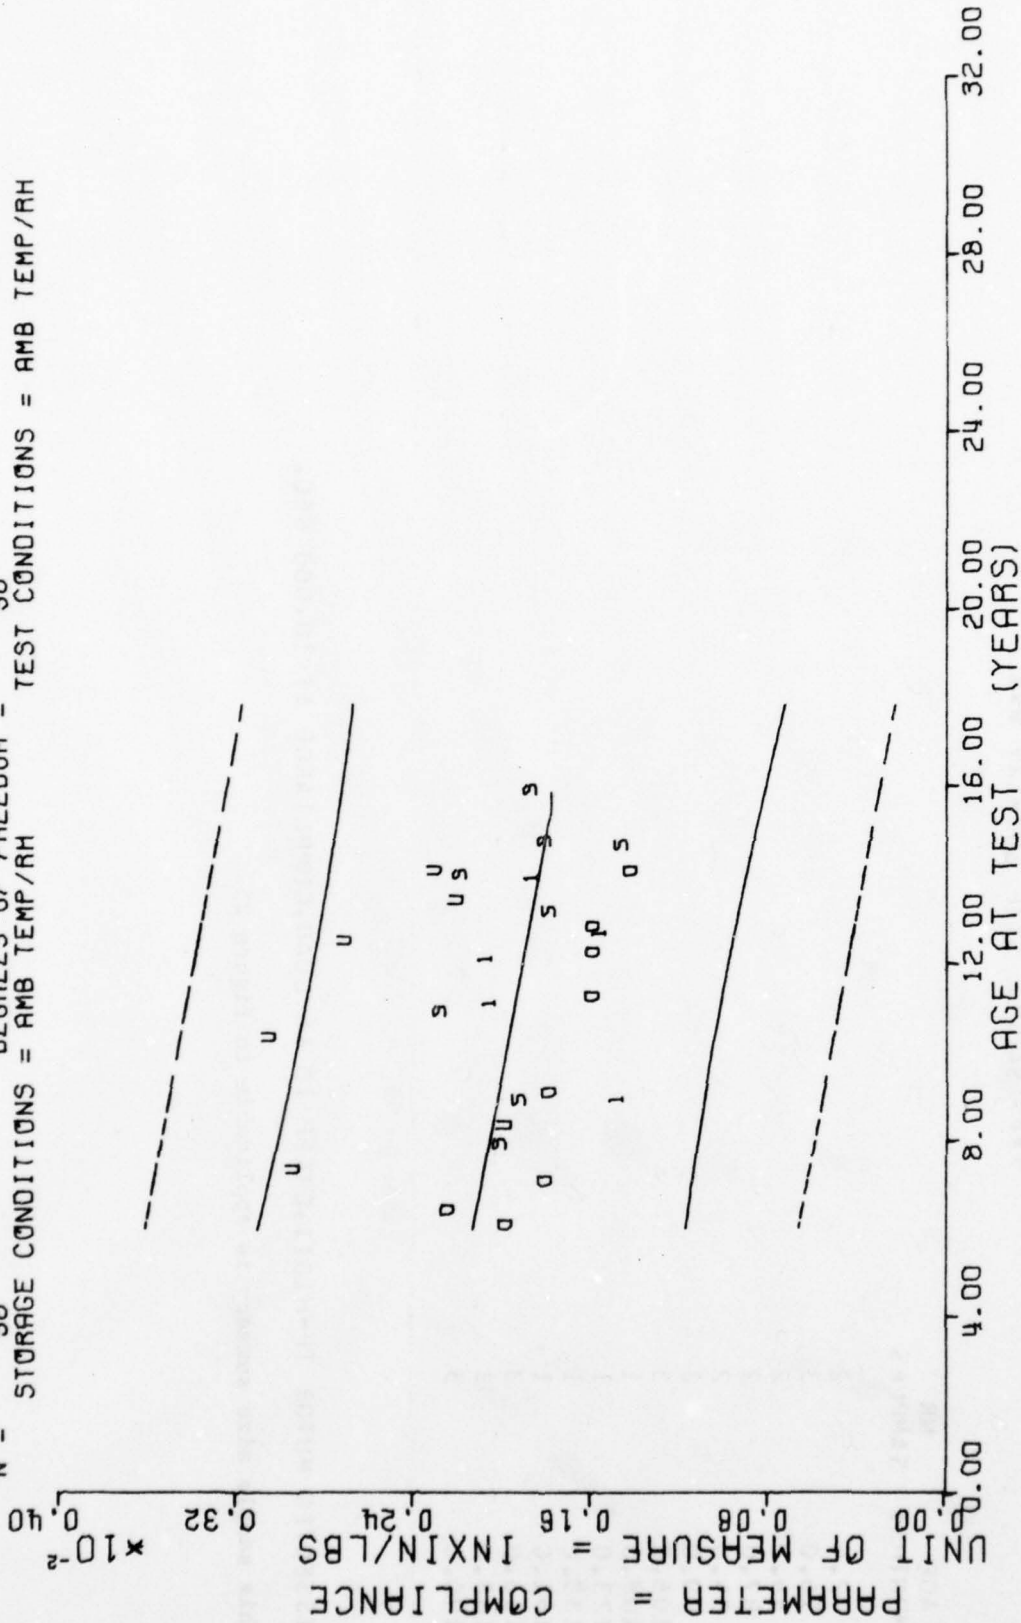

DISSECTED MOTOR 7P-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 1000 SEC

Figure 24

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
151.0	1
166.0	3
168.0	3
190.0	3

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10,000 SEC.


This sample size summary is applicable to figure 25.

$F = +5.2715154E+00$
 $R = -4.0416440E-01$
 $I = +2.2959780E+00$
 $N =$

$Y = ((+3.3347181E-03) + (-5.7786479E-06) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF I = SIGNIFICANT
 DEGREES OF FREEDOM = 27

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

$\sigma = +5.8681405E-04$
 $S_0 = +2.5168567E-06$
 $S_e = +5.4660027E-04$

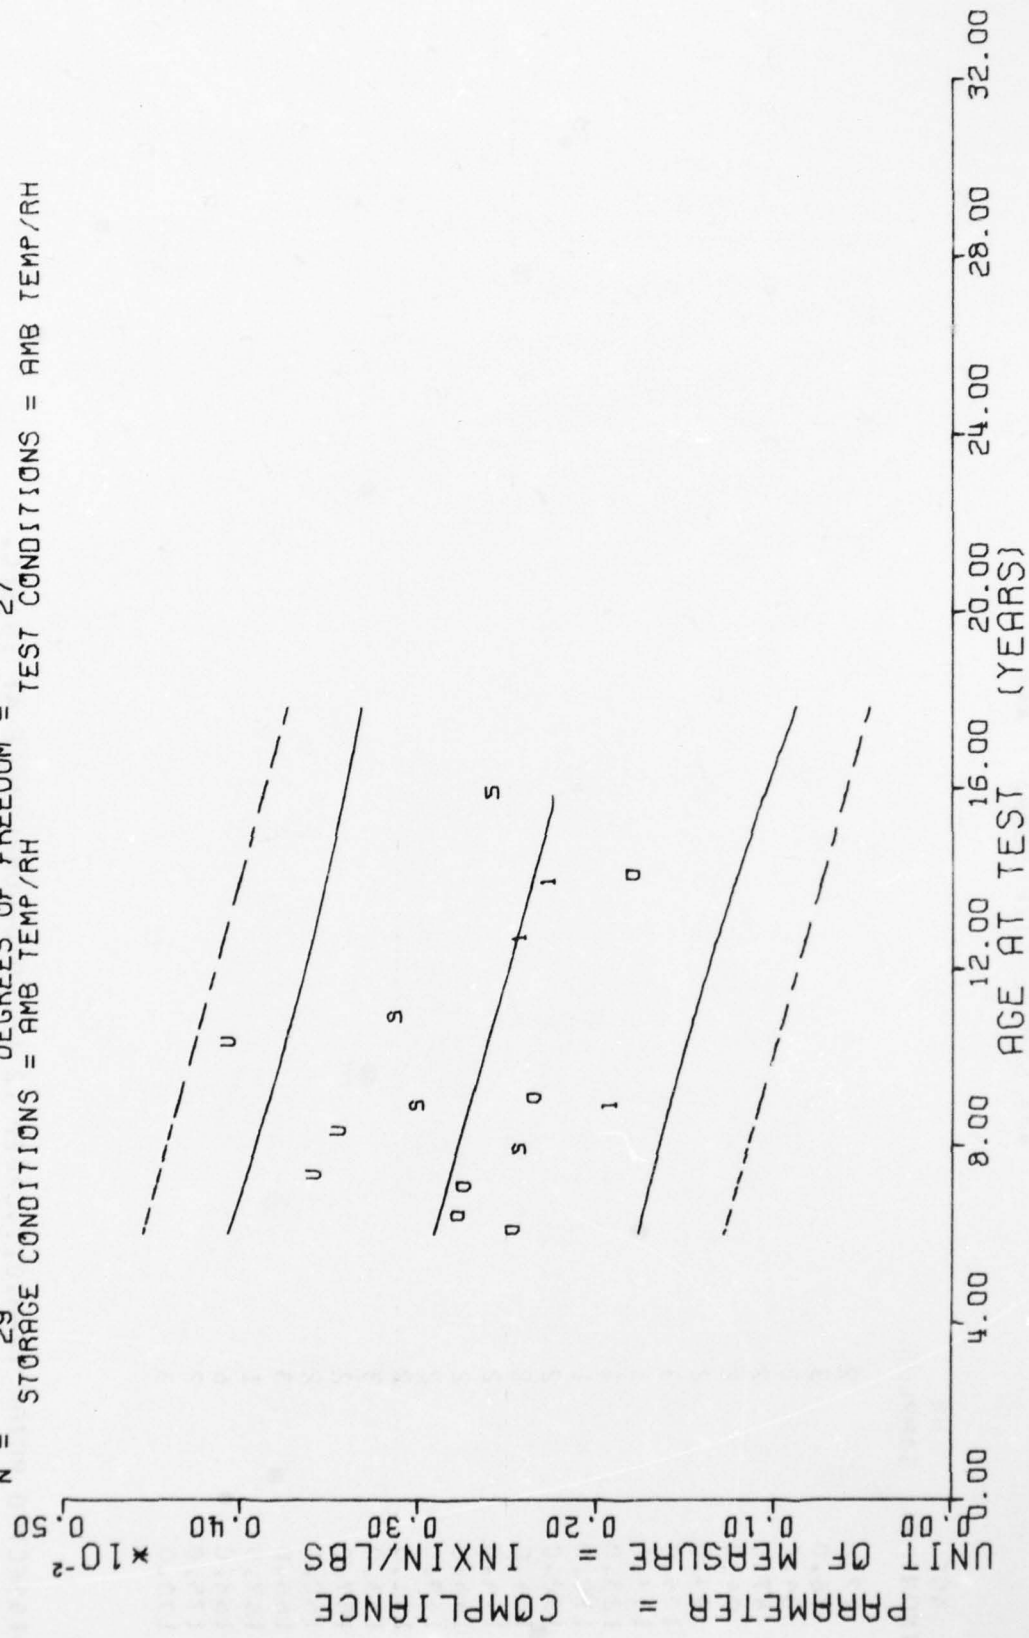

DISSECTED MOTOR TP-H1011, CREEP 10 LB LOAD, COMPLIANCE AT 10,000 SEC.

Figure 25


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	2
76.0	3
84.0	2
87.0	2
94.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
132.0	2
134.0	2
144.0	2
146.0	2
149.0	2
151.0	2
153.0	3
157.0	2
160.0	2
166.0	3
167.0	1
168.0	6
175.0	2
190.0	3

DISSECTED MOTOR TP-H1011, CREEP 12 LB LOAD, COMPLIANCE AT 10 SEC.

This sample size summary is applicable to figures 26 thru 28.


$F = +4.5122739E+00$ SIGNIFICANCE OF F = ((+1.6931521E-03) + (-2.9228175E-06) * X)
 $R = -2.8510394E-01$ SIGNIFICANT
 $t = +2.1242113E+00$ SIGNIFICANT
 $N = 53$ SIGNIFICANT
 DEGREES OF FREEDOM = 51
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

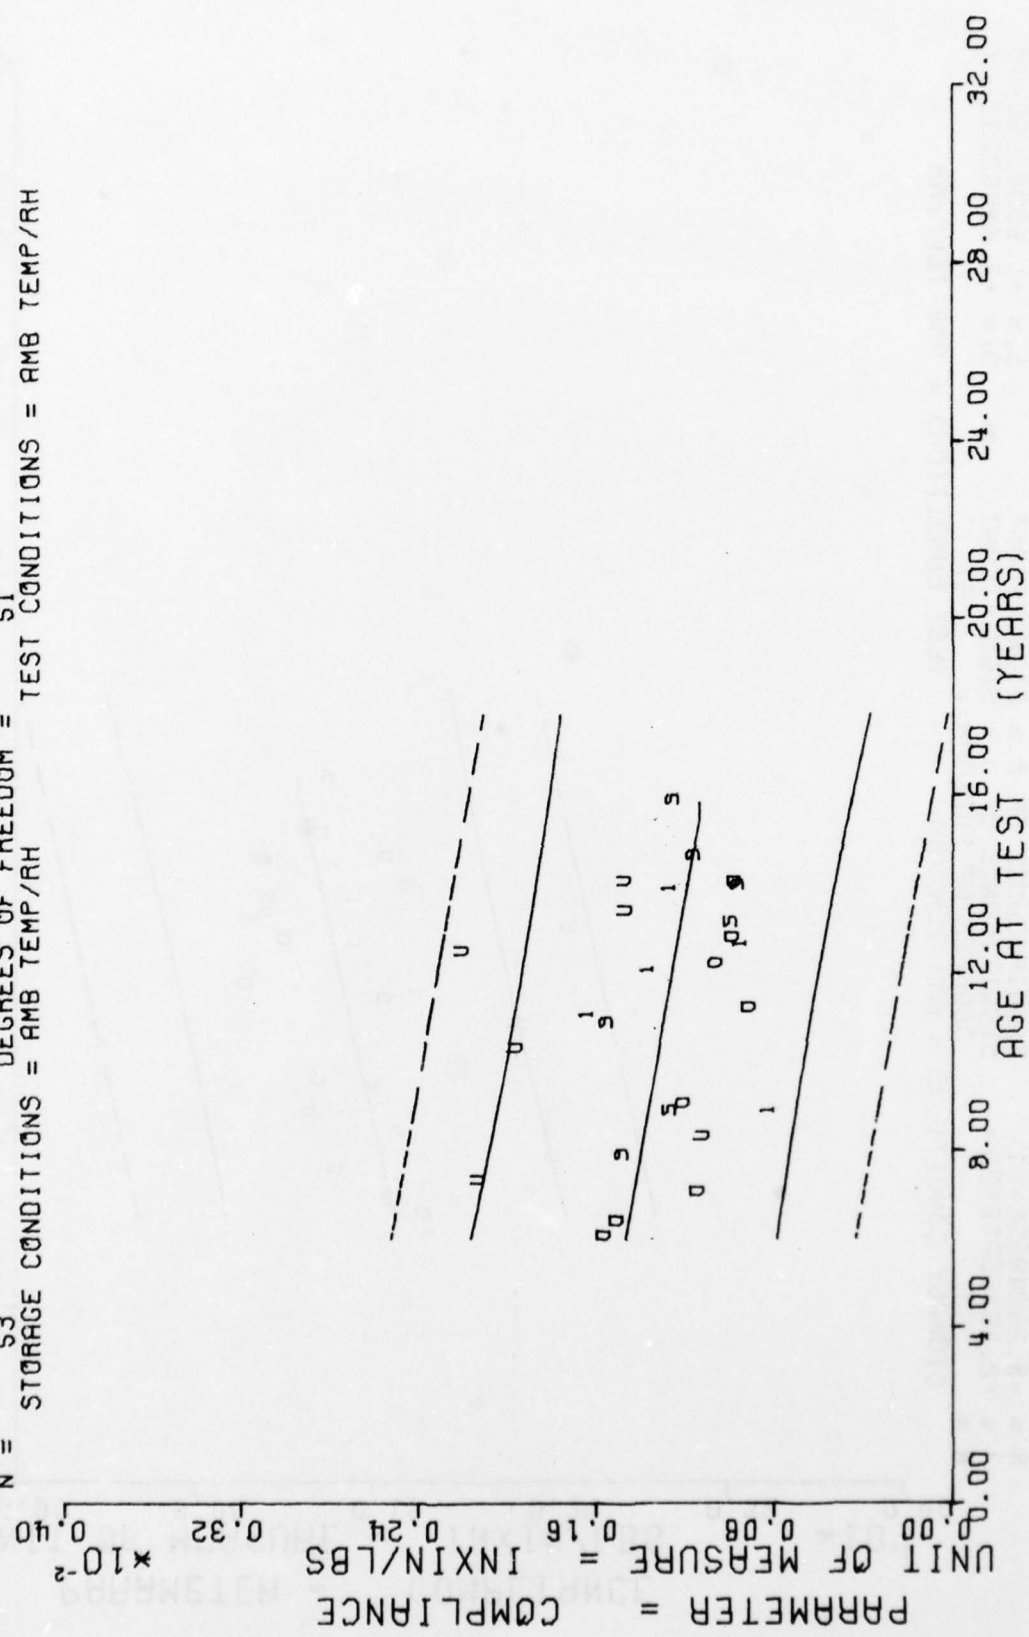

DISSECTED MOTOR TP-H1011, CREEP 12 LB LOAD, COMPLIANCE AT 10 SEC.

Figure 26

$Y = ((+1.9888073E-03) + (-3.7685371E-06) * X)$
 $F = +6.0666768E+00$ SIGNIFICANCE OF F = SIGNIFICANT
 $R = -3.2604995E-01$ SIGNIFICANCE OF R = SIGNIFICANT
 $t = +2.4630624E+00$ SIGNIFICANCE OF t = SIGNIFICANT
 $N = 53$ DEGREES OF FREEDOM = 51
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

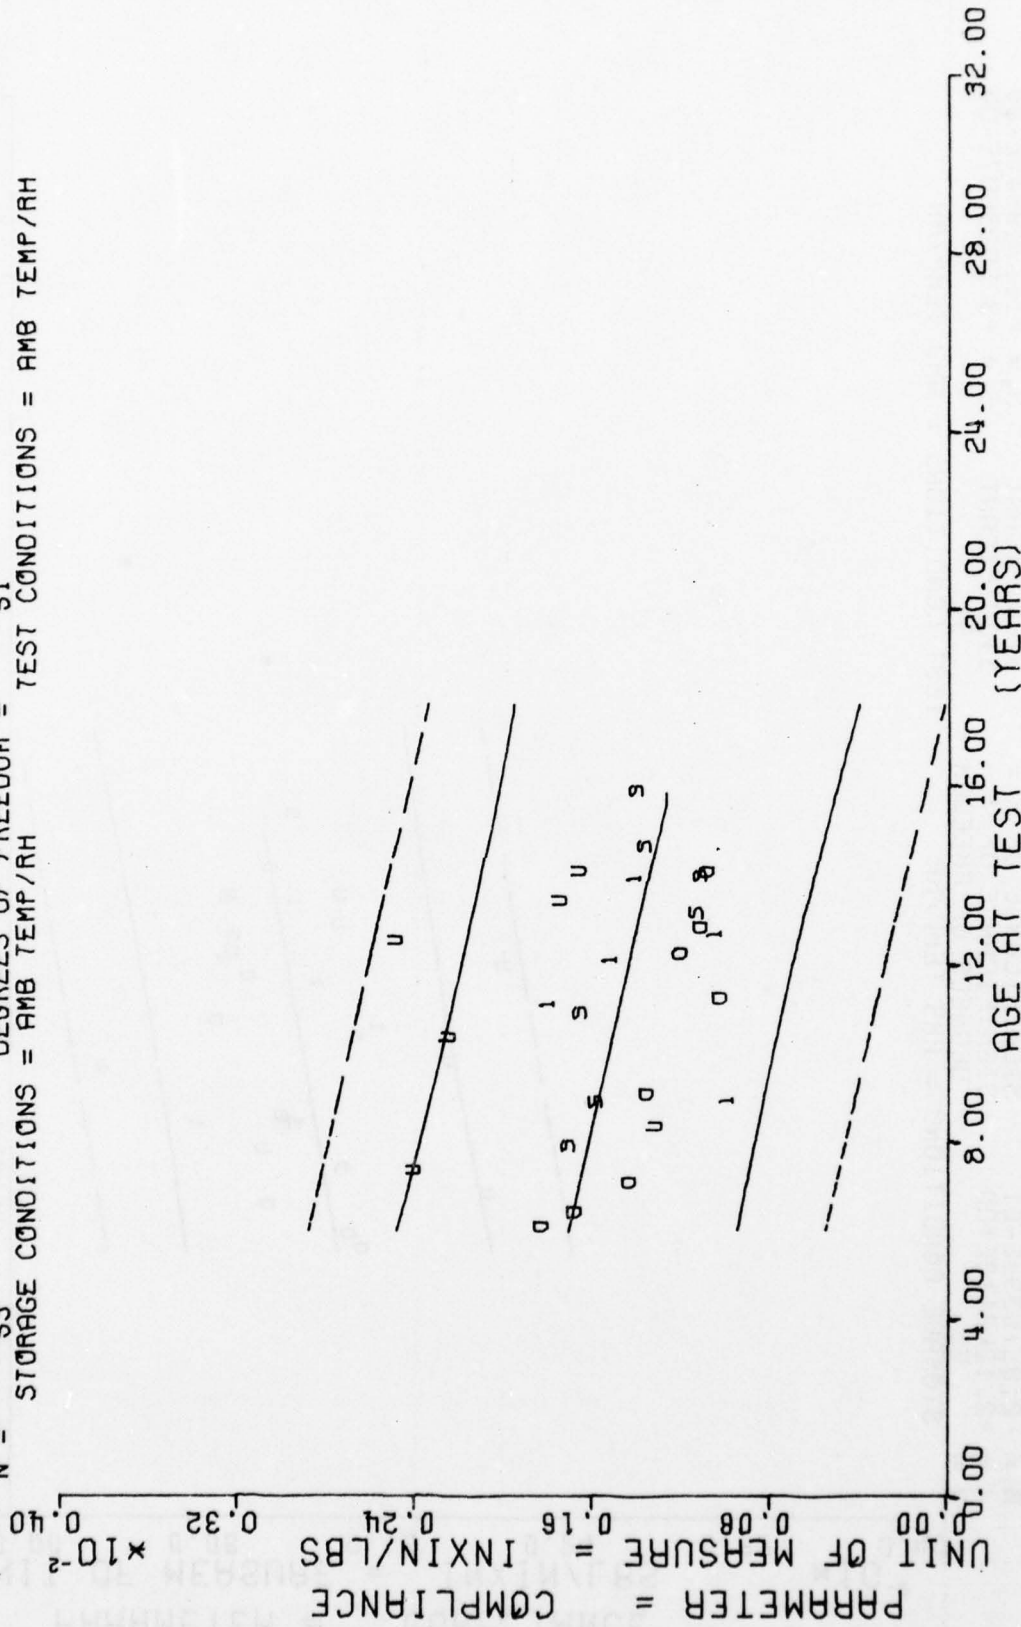

DISSECTED MOTOR TP-H1011, CREEP 12 LB LOAD, COMPLIANCE AT 20 SEC.

Figure 27


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
84.0	2
87.0	2
99.0	2
106.0	3
108.0	1
123.0	1
130.0	1
166.0	3
168.0	3
190.0	3

TP-H1011 DISSECTED MOTORS, CREEP, % STRAIN AT RUPTURE, 12 LB LOAD

This sample size summary is applicable to figure 29.

$Y = ((+2.4760104E+01) + (-1.8581941E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_f = +2.0388488E+00$
 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_e = +1.1098634E-02$
 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_f = +1.9527229E+00$
 N = 21 DEGREES OF FREEDOM = 19
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH 12 LB

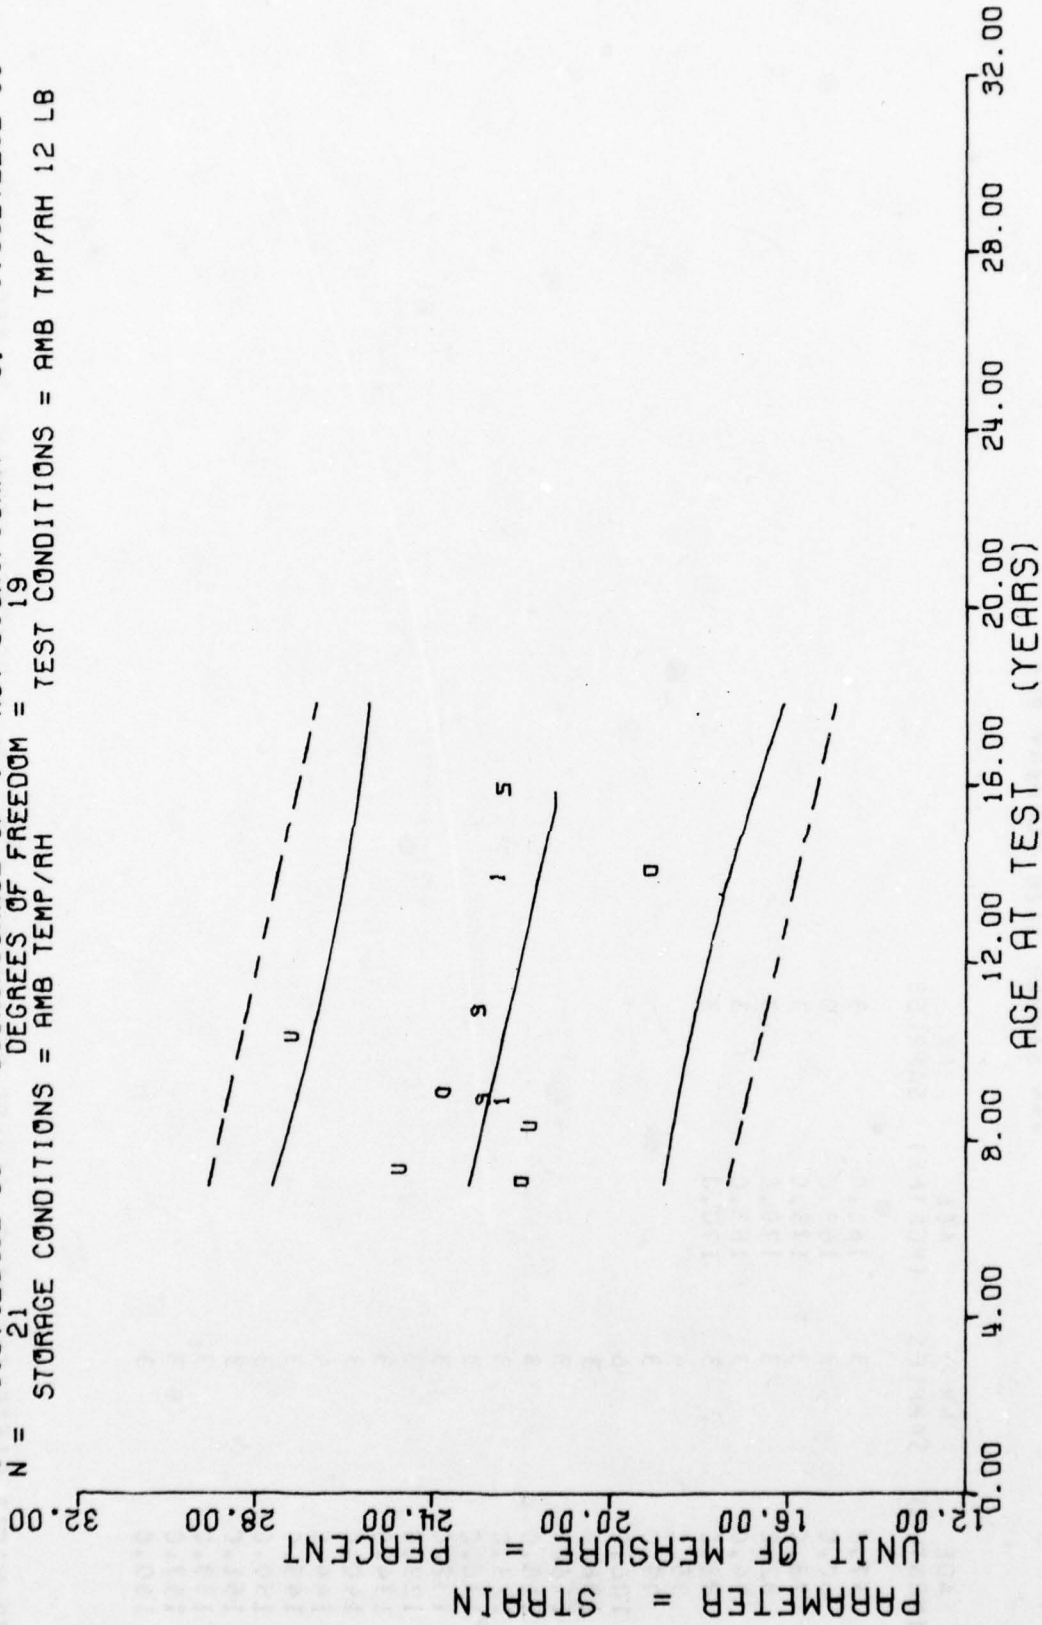

7P-H1011 DISSECTED MOTORS, CREEP, % STRAIN AT RUPTURE, 12 LB LOAD

Figure 29


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
57.0	3	166.0	3
60.0	3	168.0	9
73.0	3	175.0	3
82.0	3	175.0	3
84.0	3	183.0	3
88.0	3	190.0	3
95.0	4		
99.0	3		
106.0	6		
108.0	3		
116.0	3		
118.0	3		
123.0	3		
130.0	3		
132.0	3		
133.0	3		
134.0	3		
140.0	3		
144.0	4		
145.0	3		
150.0	3		
151.0	3		
153.0	3		
157.0	3		
160.0	3		

TP-H1C11 DISSECTED MRS, STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 10 SEC


This sample size summary is applicable to figures 30 thru 33.

Y = ((+6.2098180E+02) + (+4.0867961E-01) * X)
 F = +1.1197324E+00 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_4 = +1.4845723E+02$
 R = +1.0272095E-01 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_4 = +3.8621207E-01$
 L = +1.0581740E+00 SIGNIFICANCE OF L = NOT SIGNIFICANT $S_1 = +1.4837345E+02$
 N = 107 DEGREES OF FREEDOM = 105
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

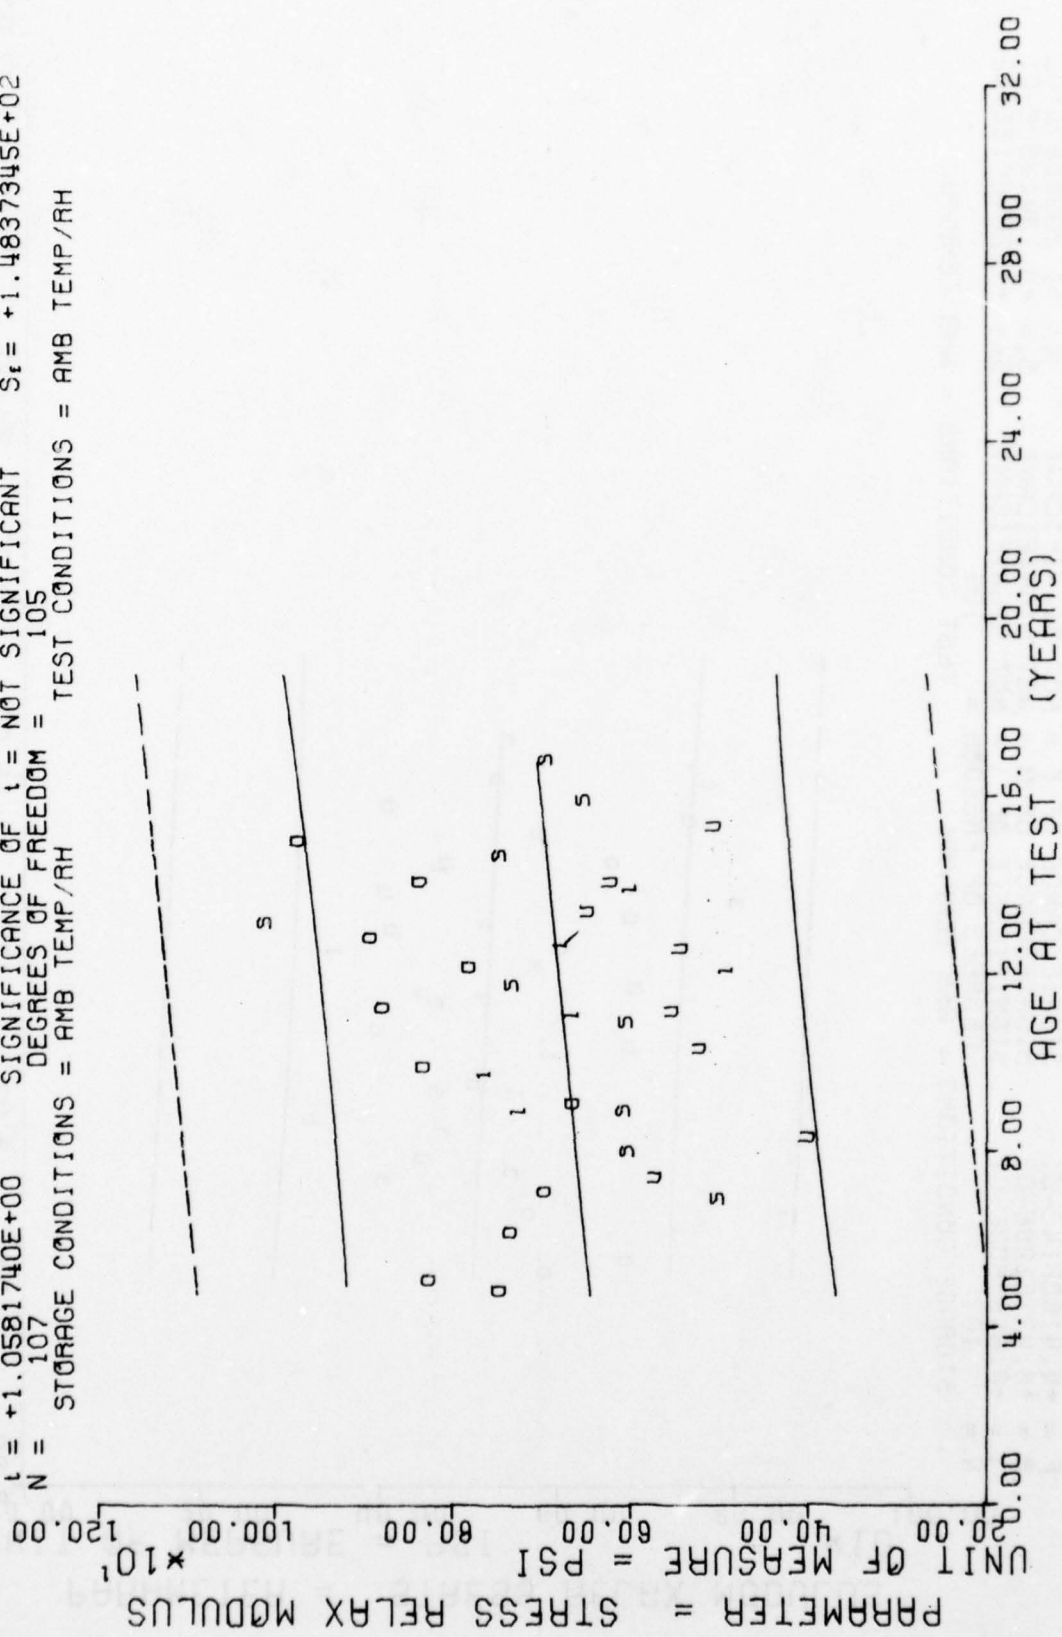

TP-H1011 DISSECTED MTRs, STRESS RELAXATION MODULUS, 3 PERCENT STRAIN, 10 SEC
Figure 30

F = +3.9489052E-01
 R = +6.1210873E-02
 I = +6.2840315E-01
 N = 107
 STORAGE CONDITIONS = AMB TEMP/RAH
 Y = ((+4.5845875E+02) + (+1.8199171E-01) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF I = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 105
 TEST CONDITIONS = AMB TEMP/RAH

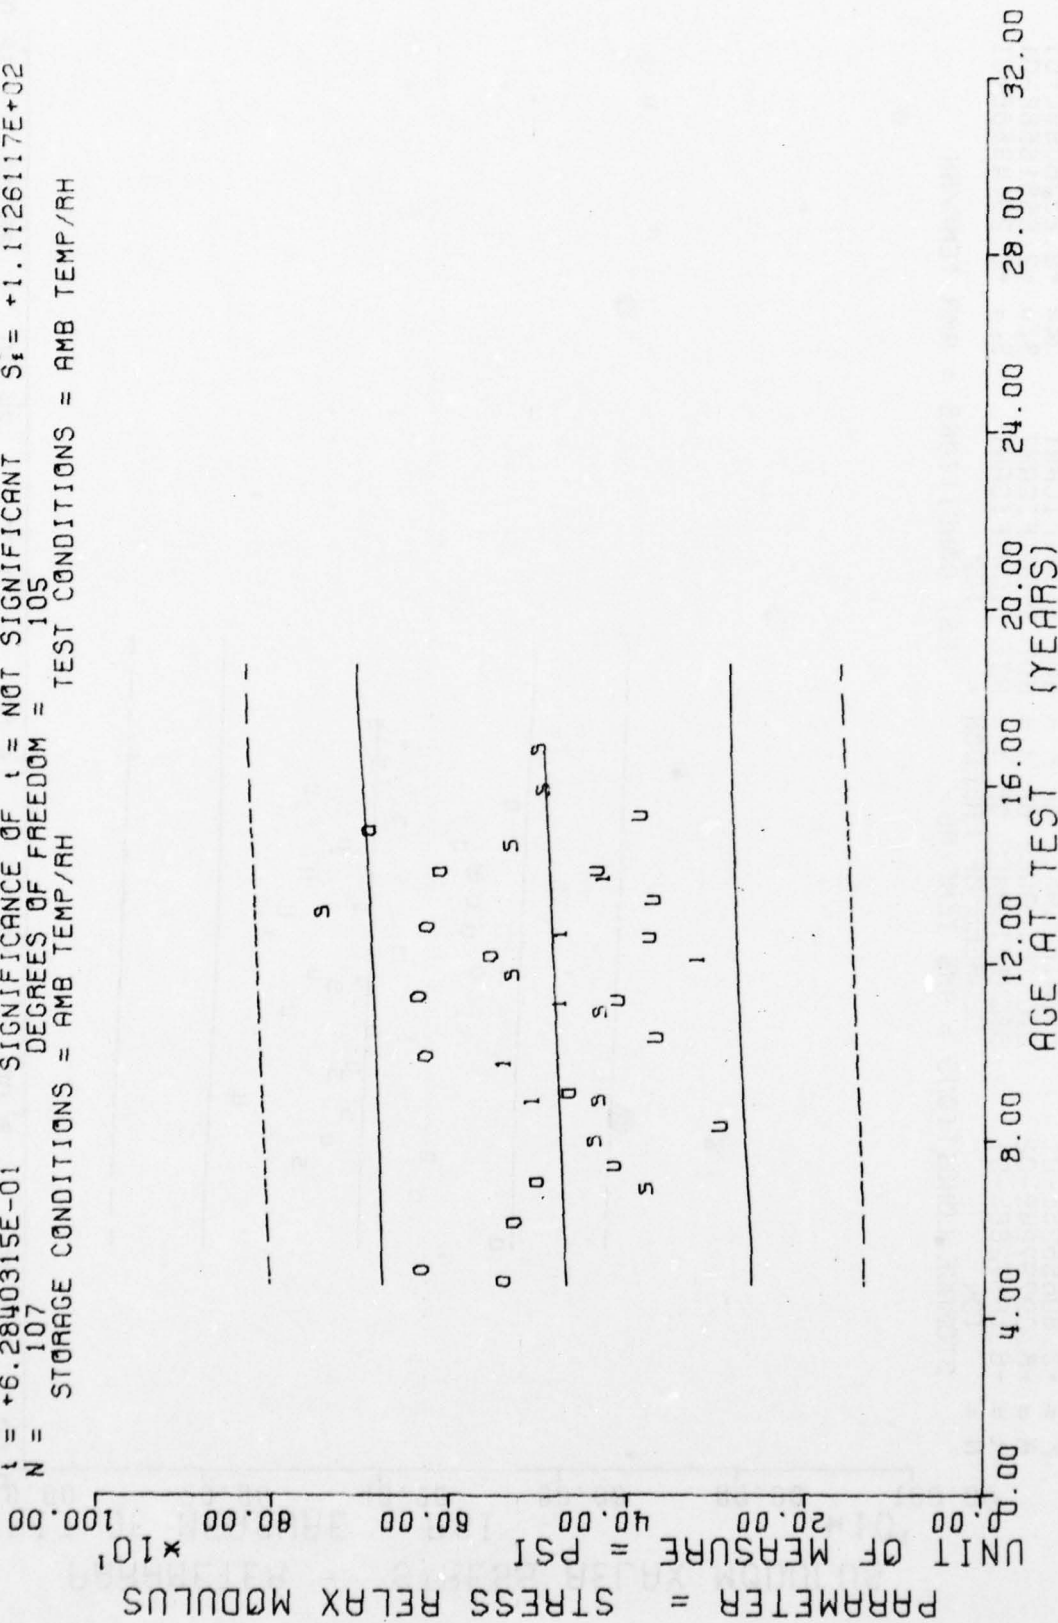


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
57.C	3	166.C	3
60.0	3	168.0	9
73.0	3	175.0	3
82.C	3	179.C	3
84.C	3	183.C	3
88.0	3	190.0	3
95.C	4		
99.C	3		
106.0	6		
108.0	3		
116.0	3		
118.C	3		
123.C	3		
130.C	3		
132.C	3		
133.C	3		
134.0	3		
140.0	3		
143.0	3		
145.C	3		
150.C	3		
151.0	3		
153.0	3		
157.C	3		
160.C	3		

TP-H1011 DISSECTED MRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 10 SEC


This sample size summary is applicable to figures 34 thru 37.

F = +3.4877762E+00
 R = +1.8013361E-01
 I = +1.8675589E+00
 N = 106
 STORAGE CONDITIONS = AMB TEMP/RH
 Y = ((+6.2981320E+02) + (+7.4345839E-01) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF I = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 104
 TEST CONDITIONS = AMB TEMP/RH

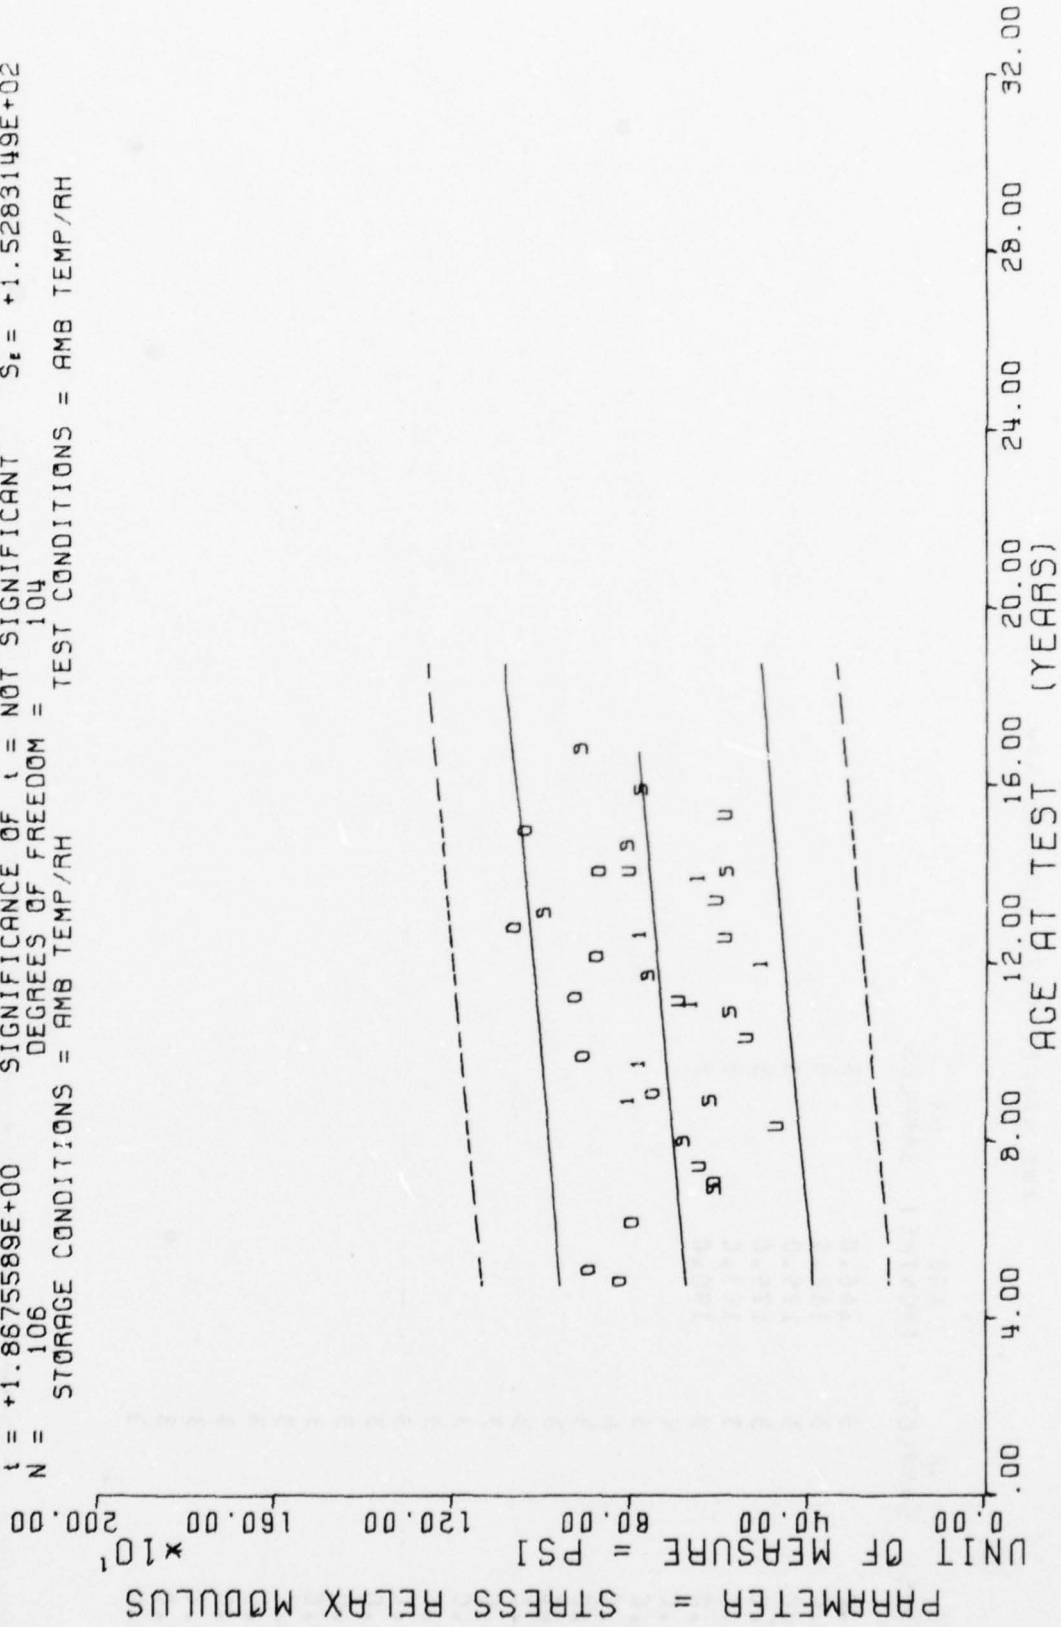


TP-H1011 DISSECTED MTRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 10 SEC
 Figure 34

F = +9.7344385E-01
 R = +9.6297659E-02
 t = +9.8663258E-01
 N = 106
 STORAGE CONDITIONS = AMB TEMP/RH
 Y = ((+4.8915541E+02) + (+2.5833542E-01) * X)
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 104
 TEST CONDITIONS = AMB TEMP/RH
 G = +1.0439943E+02
 S₁ = +2.7197097E-01
 S₂ = +1.0441263E+02

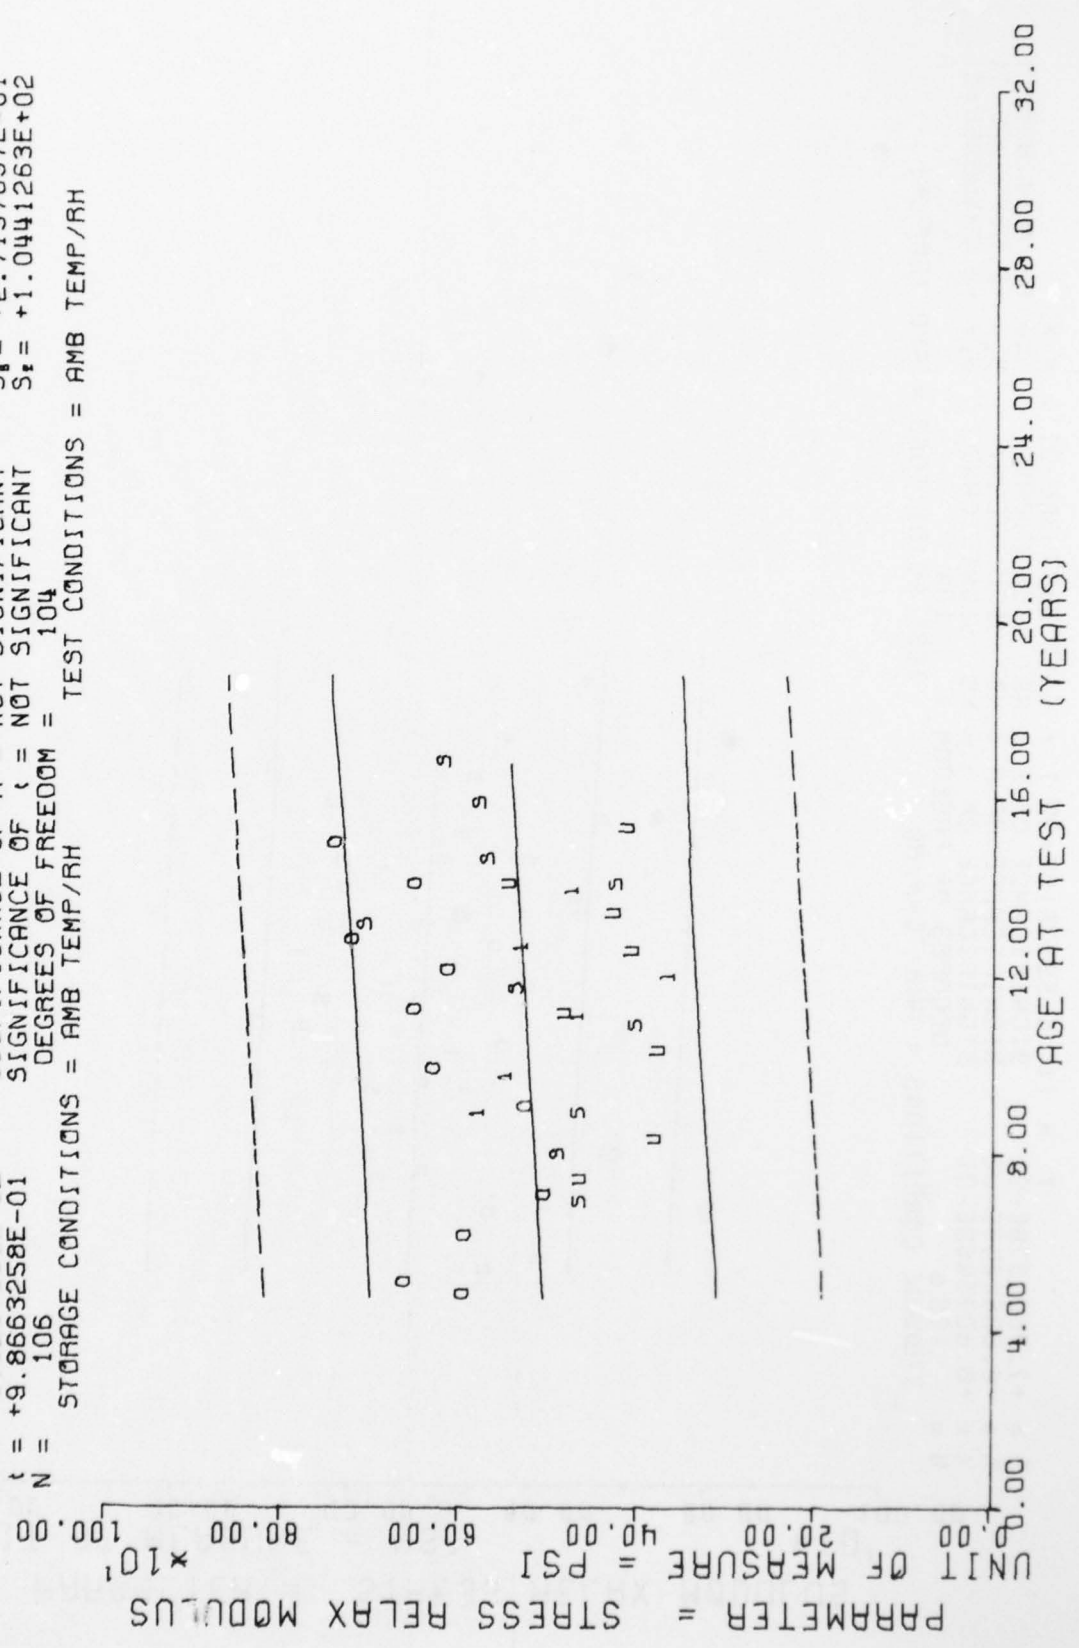

TP-H1011 BISSECTED MTRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 50 SEC
 Figure 35

Y = ((+4.5517610E+02) + (+2.2397939E-01) * X)
 F = +7.7604576E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT σ_1 = +9.7244782E+01
 R = +8.6062243E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT σ_2 = +2.5357092E-01
 I = +8.8093459E-01 SIGNIFICANCE OF I = NOT SIGNIFICANT σ_3 = +9.7348655E+01
 N = 106 DEGREES OF FREEDOM = 104
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

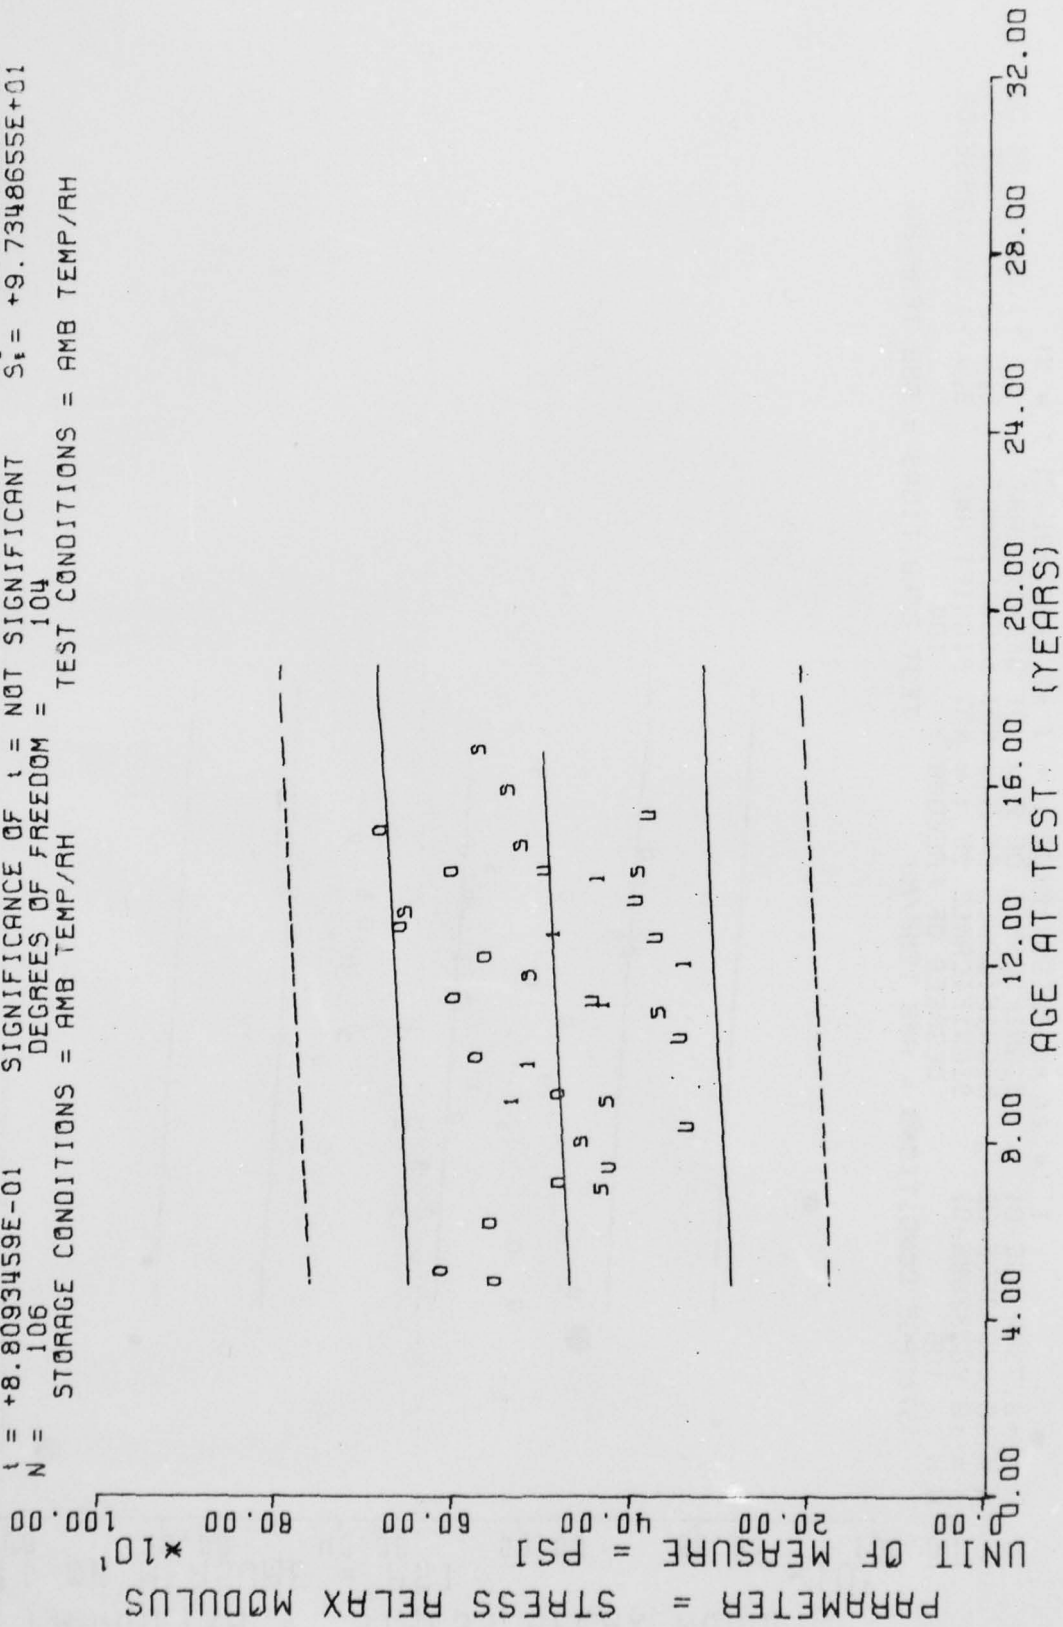

TP-H1011 DISSECTED MTRS, STRESS RELAXATION MODULUS, 5 PERCENT STRAIN, 100 SEC

Figure 36

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
72.0	16
83.0	1
94.0	1
105.0	1
107.0	1
109.0	1
117.0	1
120.0	1
131.0	1
135.0	2
137.0	2
142.0	1
159.0	2

STAGE 1 DSSCTD MTRS, CONSTANT STRAIN, STRAIN 0.1 INIT AND 0.01 EVERY 48 HRS


This sample size summary is applicable to figure 38.

$F = +5.2947397E+01$
 $R = -8.0381244E-01$
 $t = +7.2764962E+00$
 $N = 31$

$Y = ((+3.3048871E+01) + (-1.2955493E-01) * X)$

SIGNIFICANCE OF F = SIGNIFICANT $\sigma_f = +4.9583209E+00$
 SIGNIFICANCE OF R = SIGNIFICANT $S_r = +1.7804576E-02$
 SIGNIFICANCE OF t = SIGNIFICANT $S_t = +3.0000443E+00$
 DEGREES OF FREEDOM = 29

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

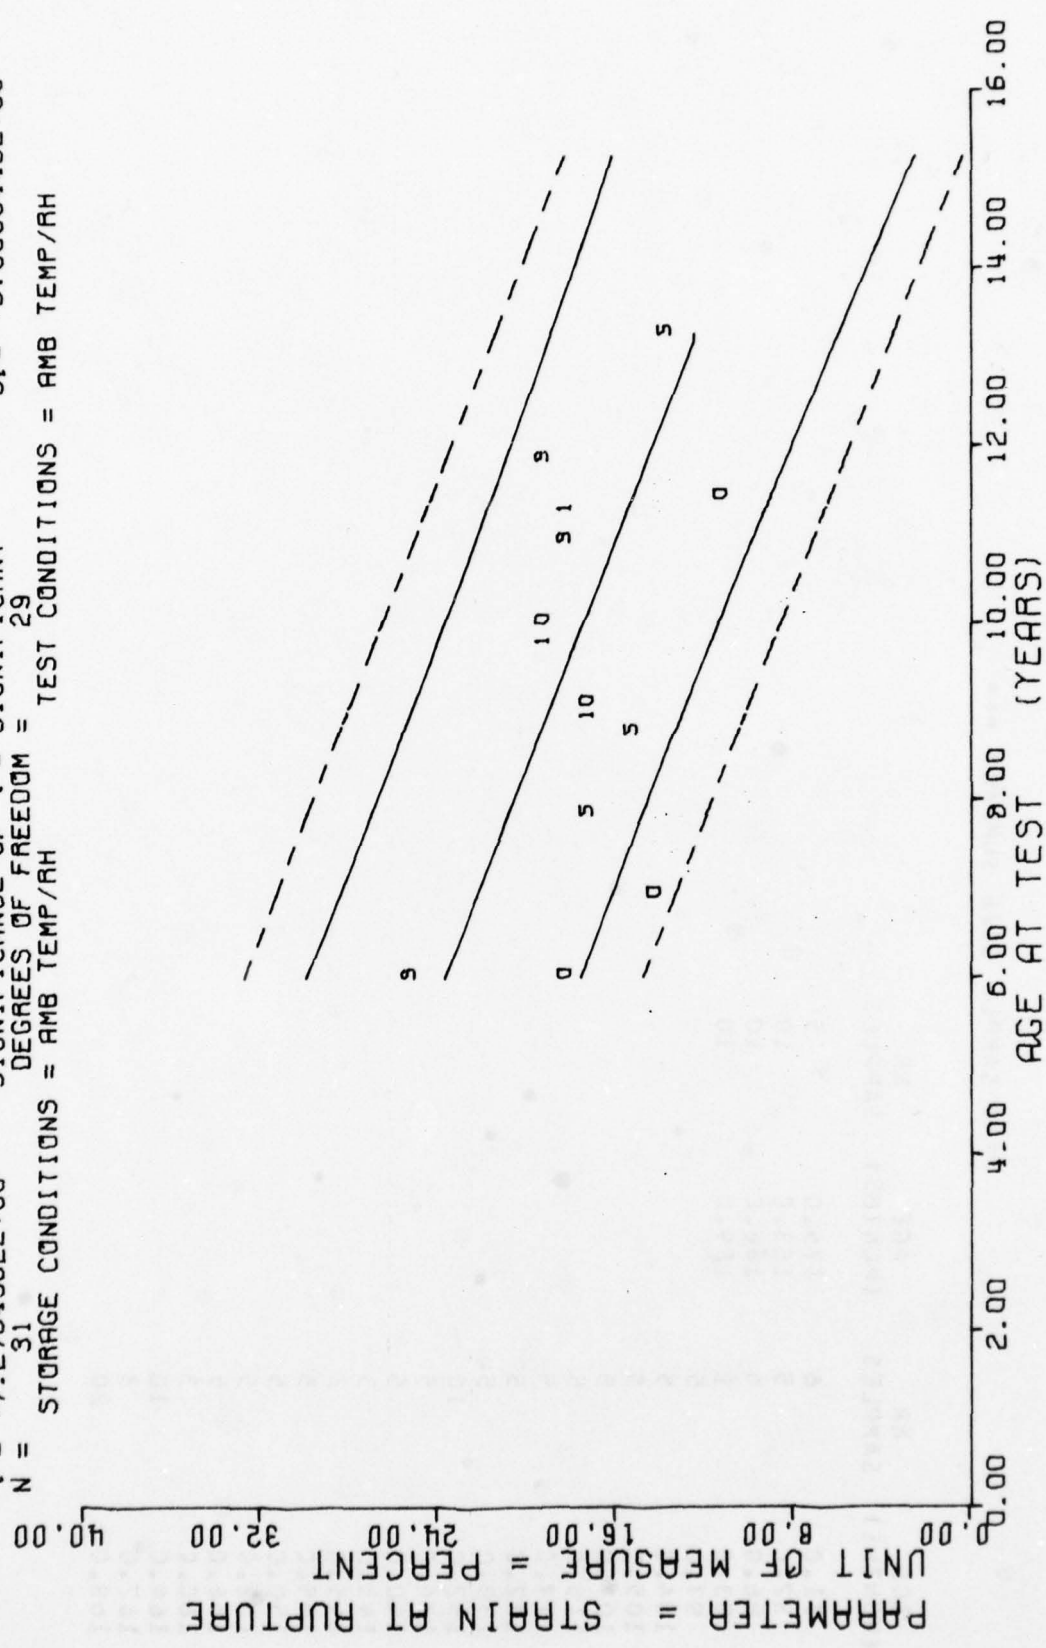

STAGE 1 OSSCTD MTRAS, CONSTANT STRAIN, STRAIN 0.1 INIT AND 0.01 EVERY 48 HRS
 Figure 38


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
71.0	6	175.0	5
82.C	5	183.C	10
86.0	6	188.C	10
93.0	1	189.0	10
97.0	5		
104.C	5		
105.C	5		
107.0	5		
115.C	5		
117.C	5		
122.C	5		
130.0	5		
132.0	10		
134.C	5		
140.C	5		
143.0	3		
145.0	3		
149.C	5		
150.C	5		
152.0	5		
156.0	5		
160.C	3		
164.C	10		
167.0	3		
168.0	20		

STAGE 1 DISSECTED MTRS, SHORE A HARDNESS, 1C SECCND

This sample size summary is applicable to figure 39.

Y = ((+6.5521867E+01) + (+5.4514864E-03) * X)
 F = +4.3875789E-01 SIGNIFICANCE OF F = NOT SIGNIFICANT σ_1 = +3.7754286E+00
 R = +4.8906537E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT S_e = +8.2300499E-03
 t = +6.6238802E-01 SIGNIFICANCE OF t = NOT SIGNIFICANT S_f = +3.7811997E+00
 N = 185 DEGREES OF FREEDOM = 183
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = 9MB TEMP/RH

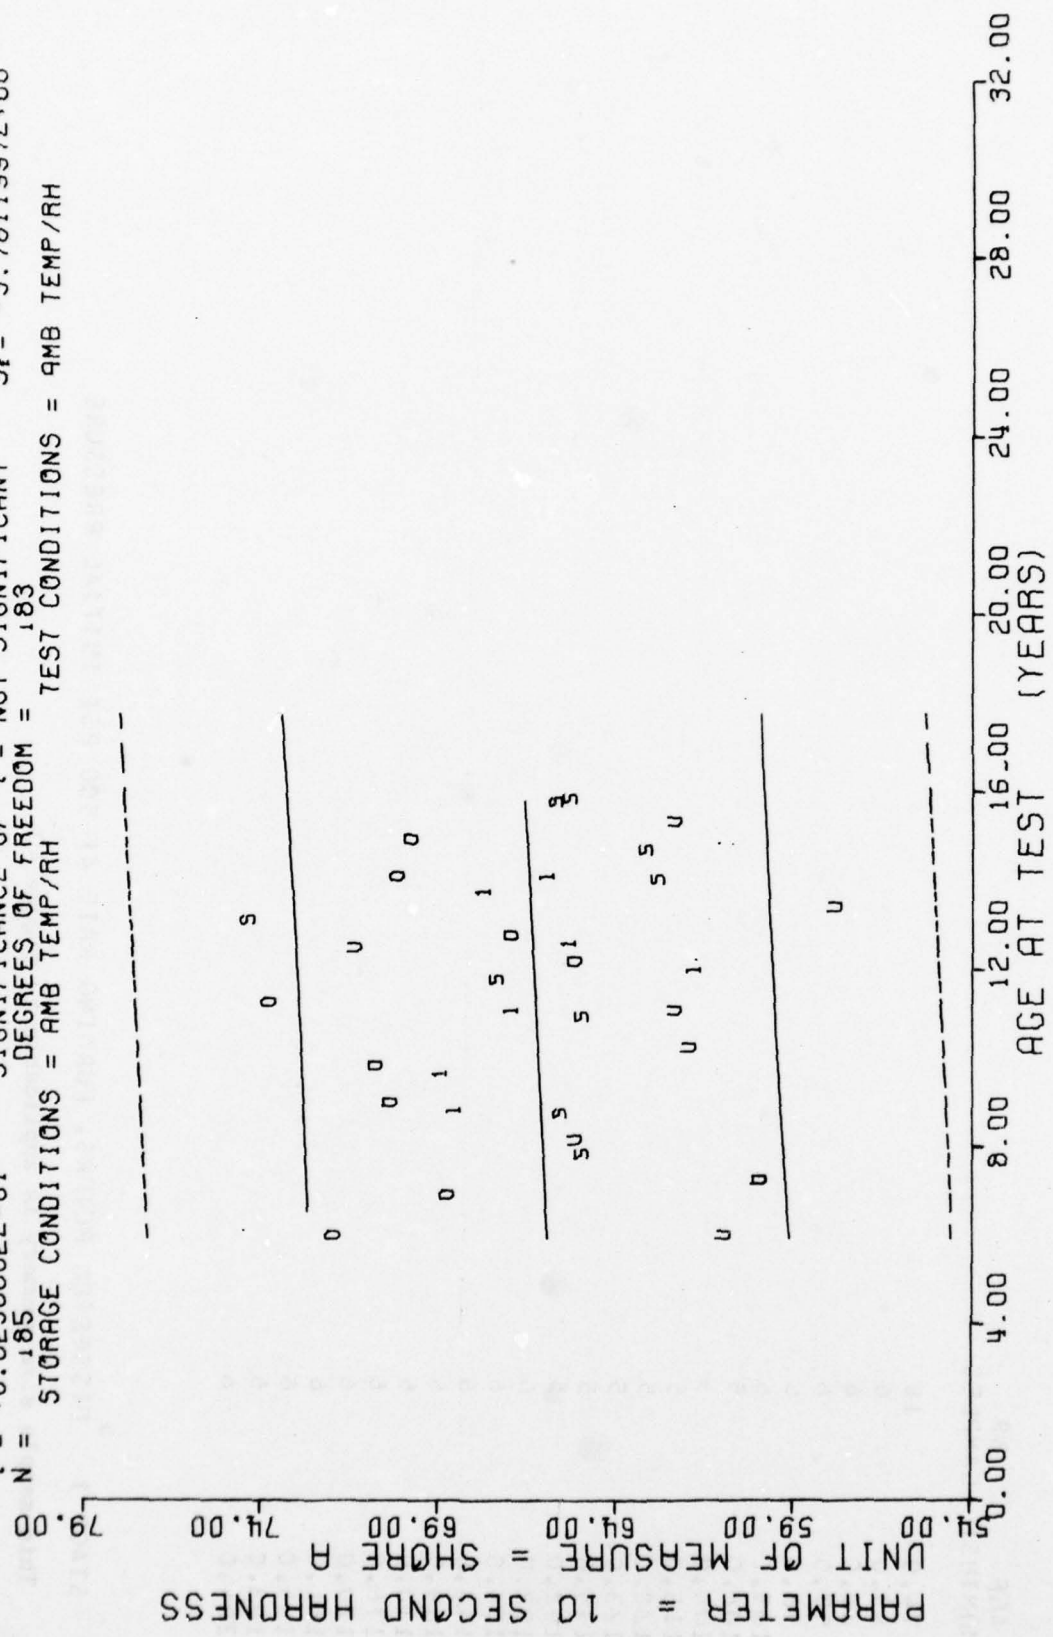

STAGE 1 DISSECTED MTRS, SHORE A HARDNESS, 10 SECOND
 Figure 39


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
74.0	18
83.0	6
89.0	6
97.0	6
98.0	6
105.0	6
106.0	5
108.0	5
118.0	5
120.0	5
123.0	5
135.0	5
142.0	5
152.0	6
154.0	6
168.0	6
169.0	6
170.0	6
176.0	6
179.0	6
181.0	6
185.0	6
193.0	6
204.0	6

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 500 PSI INITIAL PRESSURE

This sample size summary is applicable to figure 40.

$Y = ((+2.9725563E-01) + (-3.1024938E-04) * X)$
 F = +1.0943720E+02 SIGNIFICANCE OF F = SIGNIFICANT
 R = -6.5326889E-01 SIGNIFICANCE OF R = SIGNIFICANT
 t = +1.0461223E+01 SIGNIFICANCE OF t = SIGNIFICANT
 N = 149 DEGREES OF FREEDOM = 147
 STORAGE CONDITIONS = AMB TEMP/AH TEST CONDITIONS = AMB TEMP/AH

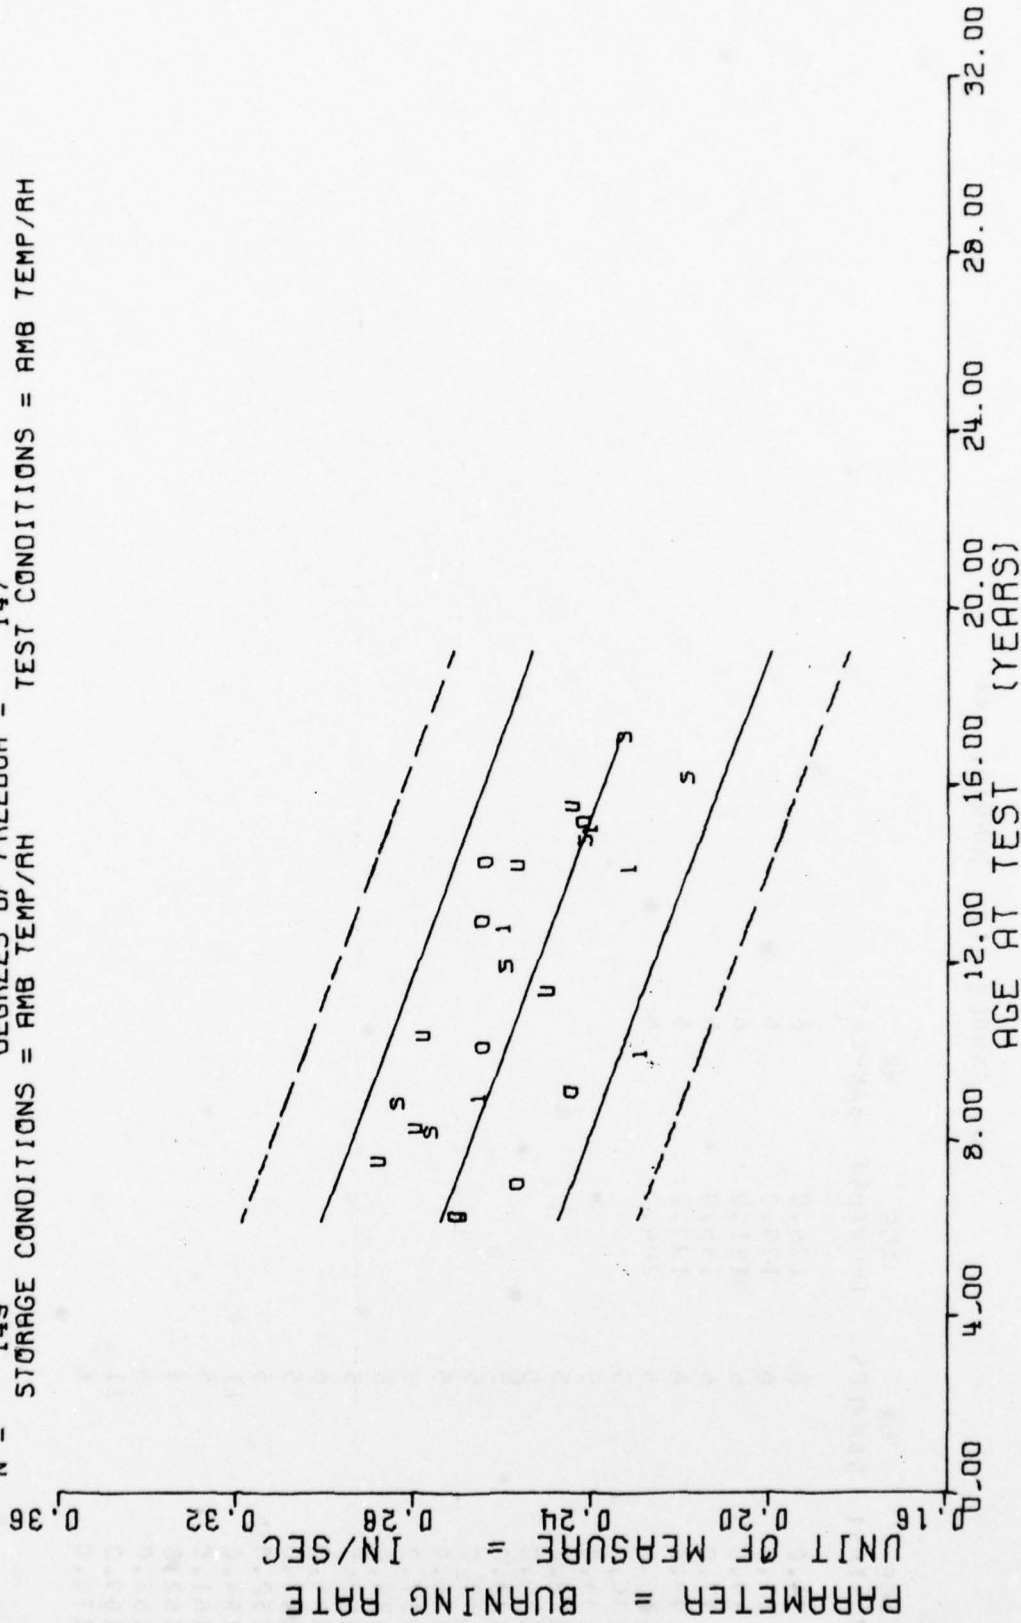

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 500 PSI INITIAL PRESSURE

Figure 40

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES	AGE (MONTHS)	NR SAMPLES
74.0	6	176.0	6
83.0	6	179.0	6
89.0	6	181.0	6
97.0	6	185.0	6
98.0	6	193.0	6
105.0	6	204.0	6
106.0	5		
108.0	5		
118.0	5		
120.0	5		
123.0	5		
130.0	5		
135.0	5		
137.0	8		
139.0	5		
142.0	5		
145.0	6		
147.0	5		
152.0	5		
154.0	11		
161.0	5		
162.0	5		
158.0	6		
163.0	11		
170.0	6		

STAGE 1 DISSECTED MOTORS, BURNING RATE AT 1000 PSI INITIAL PRESSURE

This sample size summary is applicable to figure 41.

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
74.0	3
76.0	3
83.0	3
91.0	3
98.0	6
105.0	3
108.0	1
110.0	1
125.0	1
132.0	1
136.0	3
138.0	3
152.0	3
153.0	3
154.0	3
160.0	3
167.0	3
169.0	6
175.0	3
176.0	3
184.0	3
191.0	3
200.0	3

STAGE 1 DISSECTED MOTORS, HEAT OF EXPLOSION


This sample size summary is applicable to figure 42.

$F = +3.0391898E+00$
 $R = +2.1114917E-01$
 $t = +1.7416055E+00$
 $N = 67$

$Y = ((+1.5410055E+03) + (+4.8457936E-02) * X)$
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 DEGREES OF FREEDOM = 65

$\sigma = +8.9653095E+00$
 $S_e = +2.7823715E-02$
 $S_t = +8.8303280E+00$

STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

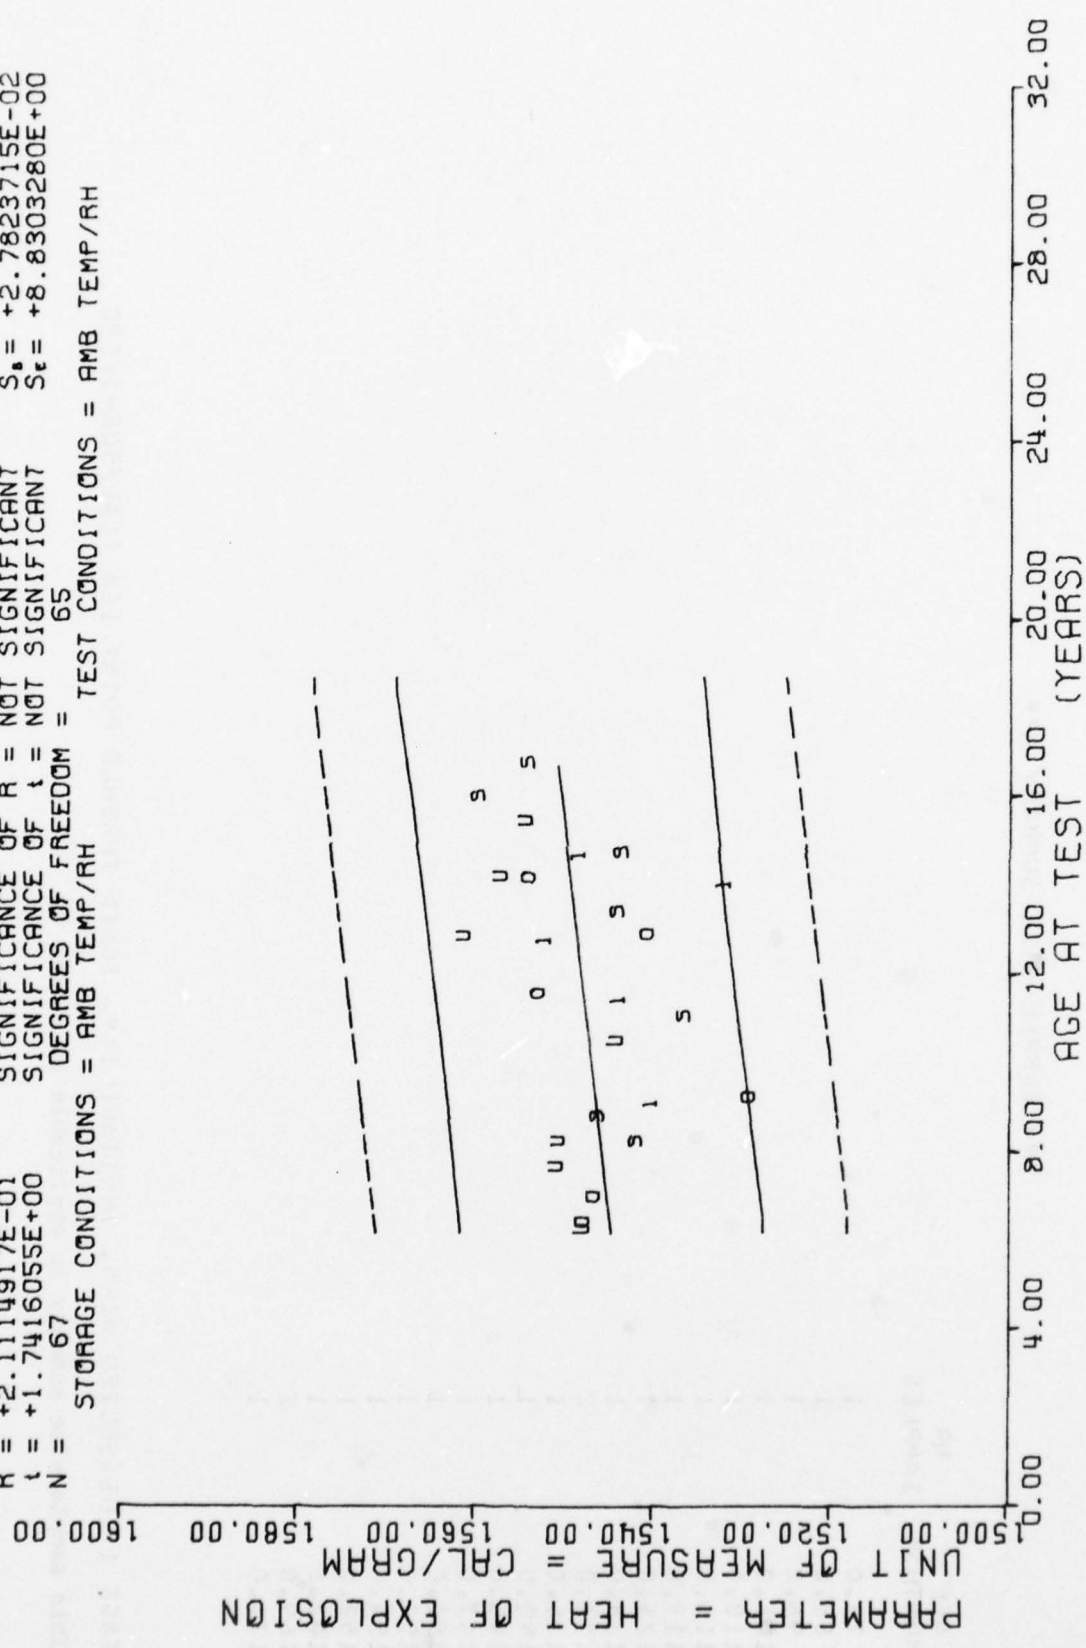

STAGE 1 DISSECTED MOTORS, HEAT OF EXPLOSION

Figure 42


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	1
88.0	1
96.0	1
108.0	1
110.0	1
116.0	1
118.0	1
125.0	1
133.0	1
134.0	2
136.0	1
140.0	1
145.0	1
147.0	1
151.0	1
152.0	1
154.0	1
158.0	1
162.0	1
169.0	2
176.0	1

STAGE 1 DISSECTED MTRS, IGNITABILITY, IGNTN THRSOLD POINT 168 (CAL/SQCM)/SEC

This sample size summary is applicable to figure 43.

$Y = ((+5.7692488E+01) + (-3.8549585E-03) * X)$
 F = +5.6660960E-03 SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_r = +6.3507492E+00$
 R = -1.6423803E-02 SIGNIFICANCE OF R = NOT SIGNIFICANT $S_e = +5.1212708E-02$
 t = +7.5273474E-02 SIGNIFICANCE OF t = NOT SIGNIFICANT $S_r = +6.4993223E+00$
 N = 23 DEGREES OF FREEDOM = 21
 STORAGE CONDITIONS = AMB TEMP/AH TEST CONDITIONS = 168 CAL/SQCM/SEC

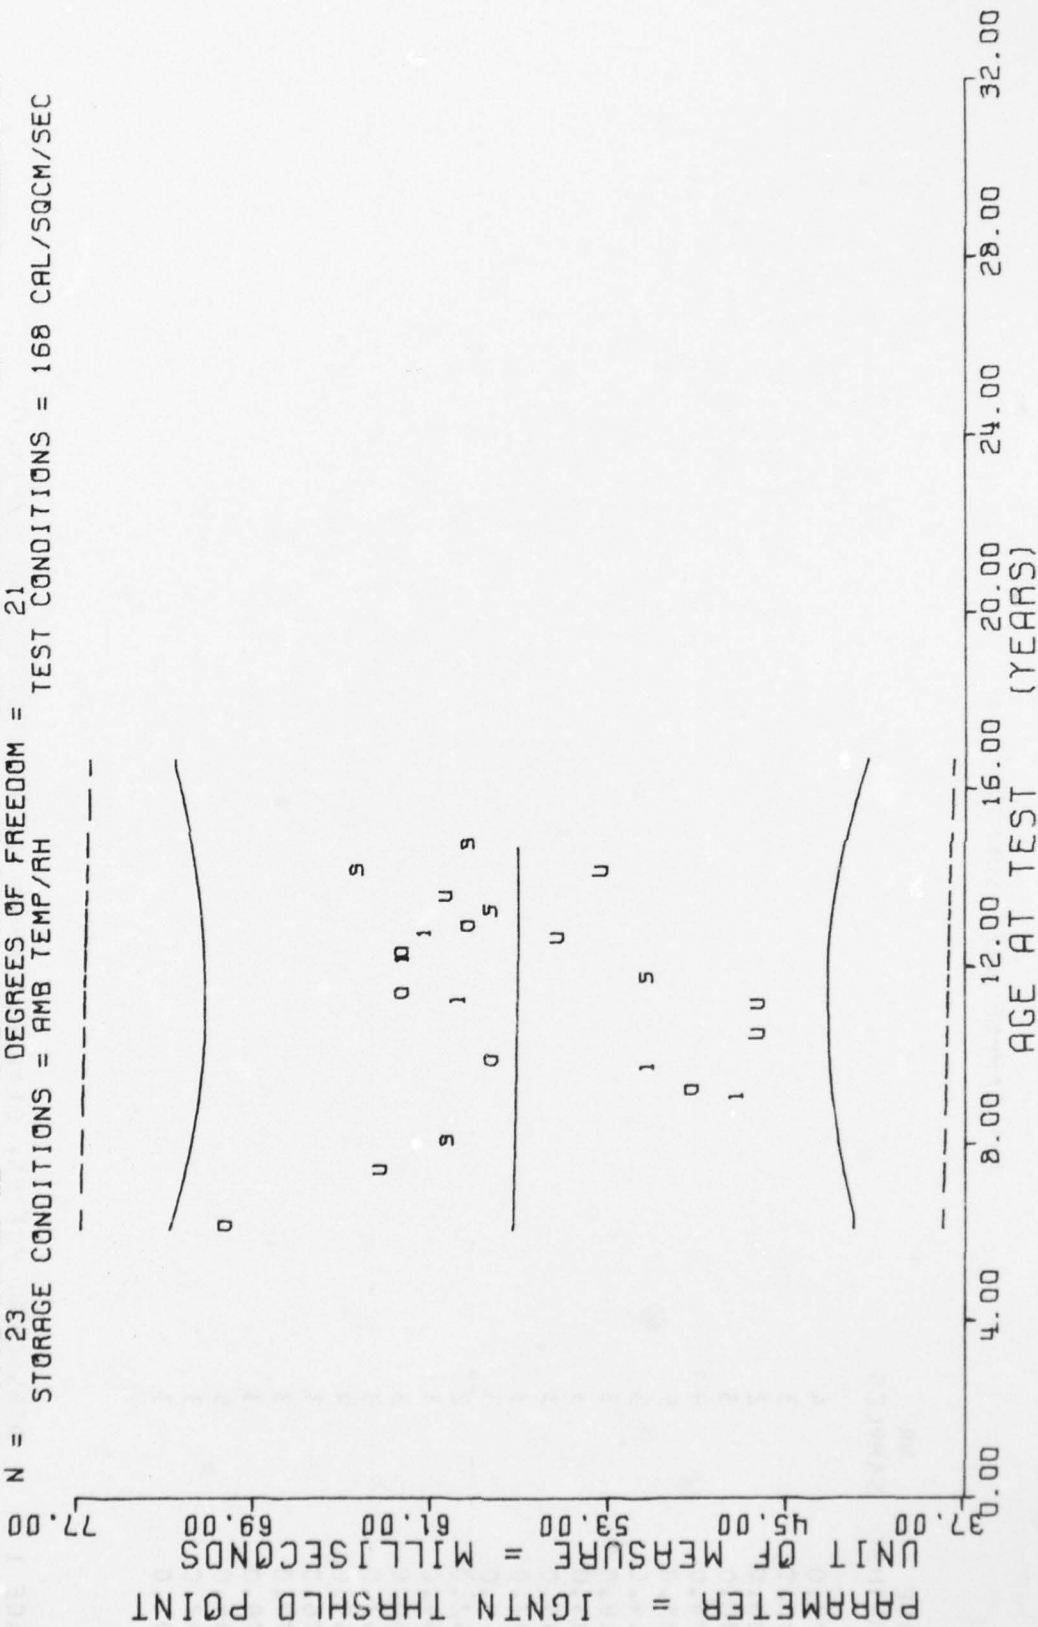

STAGE 1 DISSECTED MTRS, IGNITABILITY, IGNTN THRSOLD POINT 168 (CAL/SQCM)/SEC

Figure 43

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	4
75.0	3
83.0	2
90.0	3
98.0	9
105.0	5
114.C	3
118.0	3
133.0	3
135.0	3
137.0	3
140.0	3
152.0	2
154.0	3
160.0	3
167.0	3
169.0	9
176.C	3
177.0	3
179.0	3
184.0	5
192.C	3
201.C	3

STAGE I DISSECTED MOTORS, DTA, ENDOTHERM 1, 12 DEGREE C RISE/MINUTE

This sample size summary is applicable to figures 44 and 45.

Y = ((+2.4344465E+02) NOT SIGNIFICANT
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 SIGNIFICANCE OF FREEDOM = 82
 DEGREES OF FREEDOM = TEST CONDITIONS = AMB TEMP/RH
 Y = ((+3.8479877E+00
 SIGNIFICANCE OF F = NOT SIGNIFICANT
 SIGNIFICANCE OF R = NOT SIGNIFICANT
 SIGNIFICANCE OF t = NOT SIGNIFICANT
 SIGNIFICANCE OF FREEDOM = 82
 DEGREES OF FREEDOM = TEST CONDITIONS = AMB TEMP/RH
 N = 84
 TEST CONDITIONS = AMB TEMP/RH


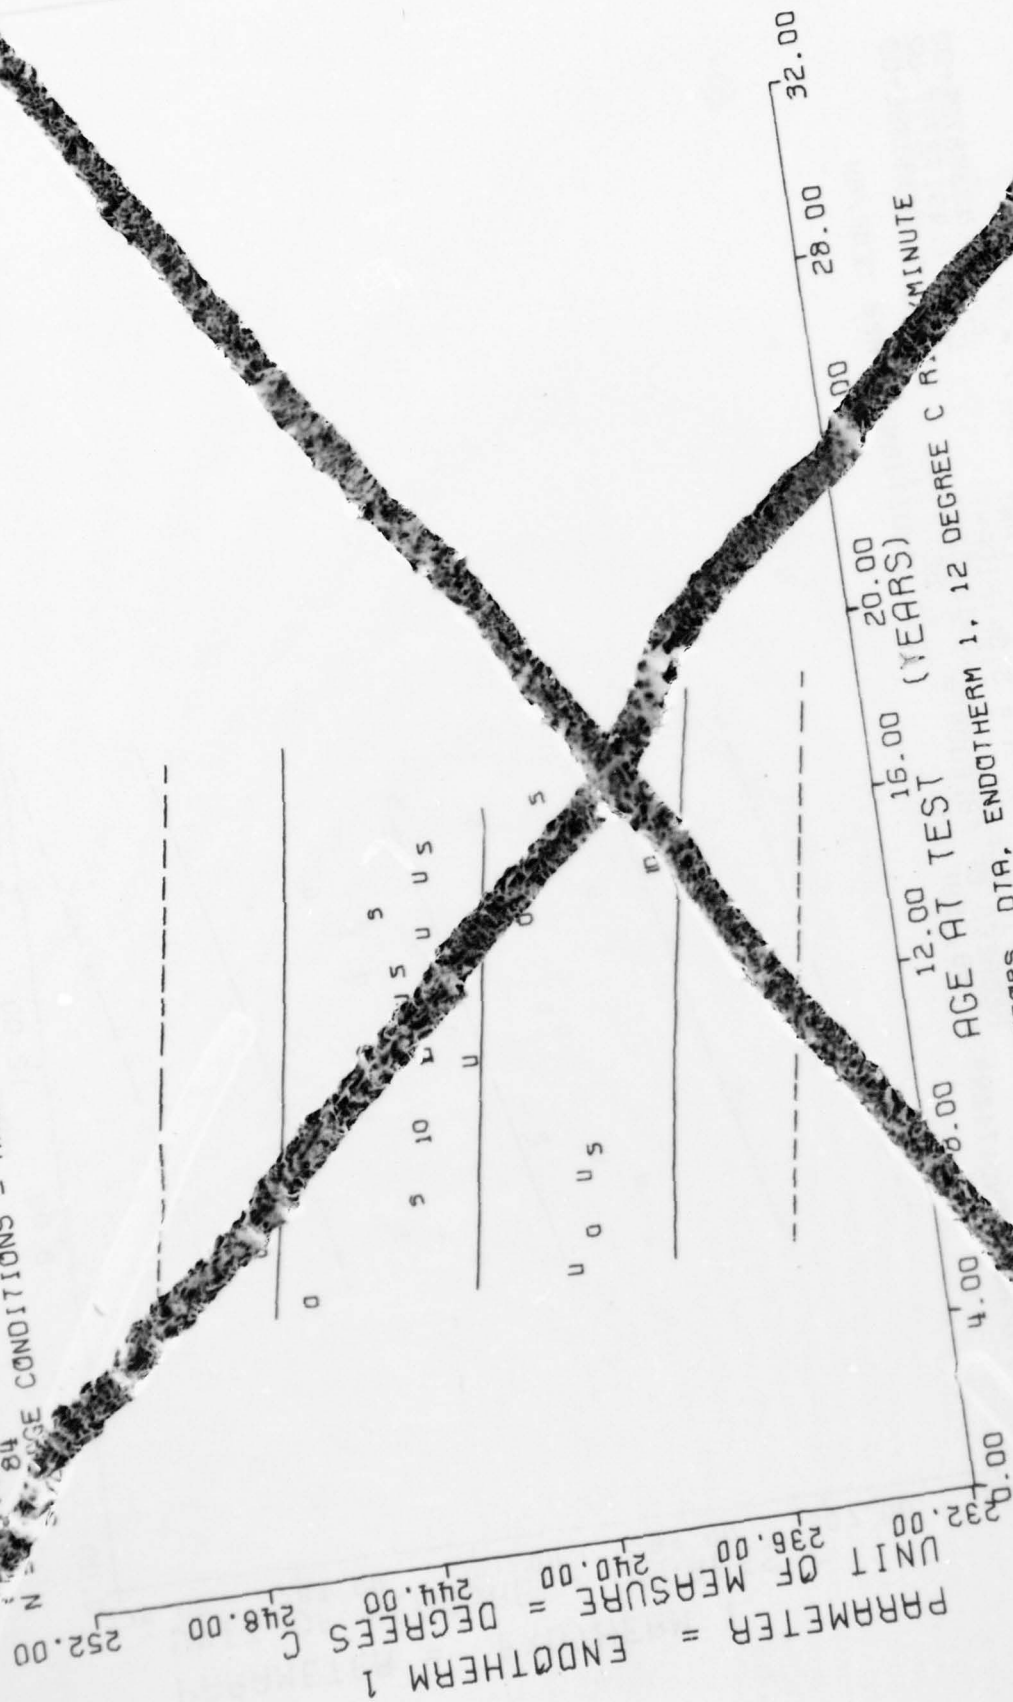


Figure 44

$F = +3.8479877E+00$ SIGNIFICANCE OF F = NOT SIGNIFICANT $\sigma_1 = +2.4607066E+00$
 $R = -2.1171507E-01$ SIGNIFICANCE OF R = NOT SIGNIFICANT $S_1 = +6.8829861E-03$
 $t = +1.9616288E+00$ SIGNIFICANCE OF t = NOT SIGNIFICANT $S_2 = +2.4195457E+00$
 $N = 84$ DEGREES OF FREEDOM = 82
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH


$$Y = ((+2.4344465E+02) + (-1.3501864E-02) * X)$$

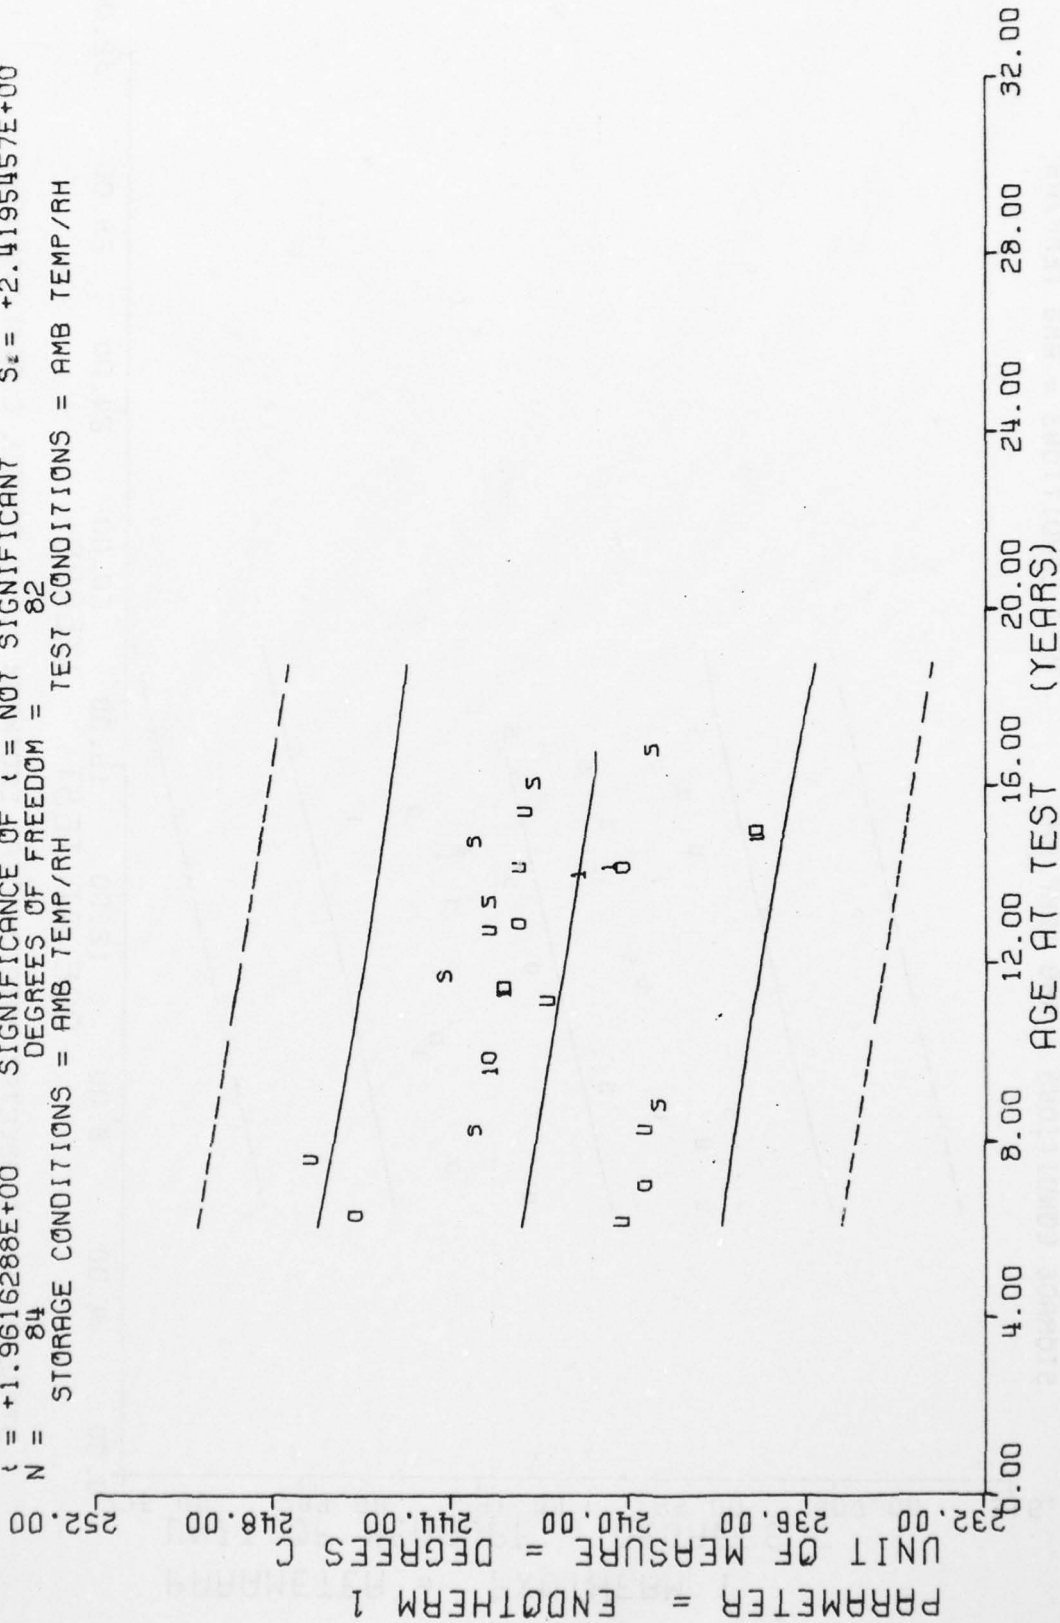

STAGE 1 DISSECTED MOTORS, DTA, ENDOTHERM 1, 12 DEGREE C RISE/MINUTE

Figure 44

$Y = ((+2.9995088E+02) + (-3.9803851E-02) * X)$
 F = +7.1198556E+00 SIGNIFICANCE OF F = SIGNIFICANT $\sigma = +5.4336872E+00$
 R = -2.8264958E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_e = +1.4917275E-02$
 t = +2.6683057E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_e = +5.2438039E+00$
 N = 84 DEGREES OF FREEDOM = 82
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

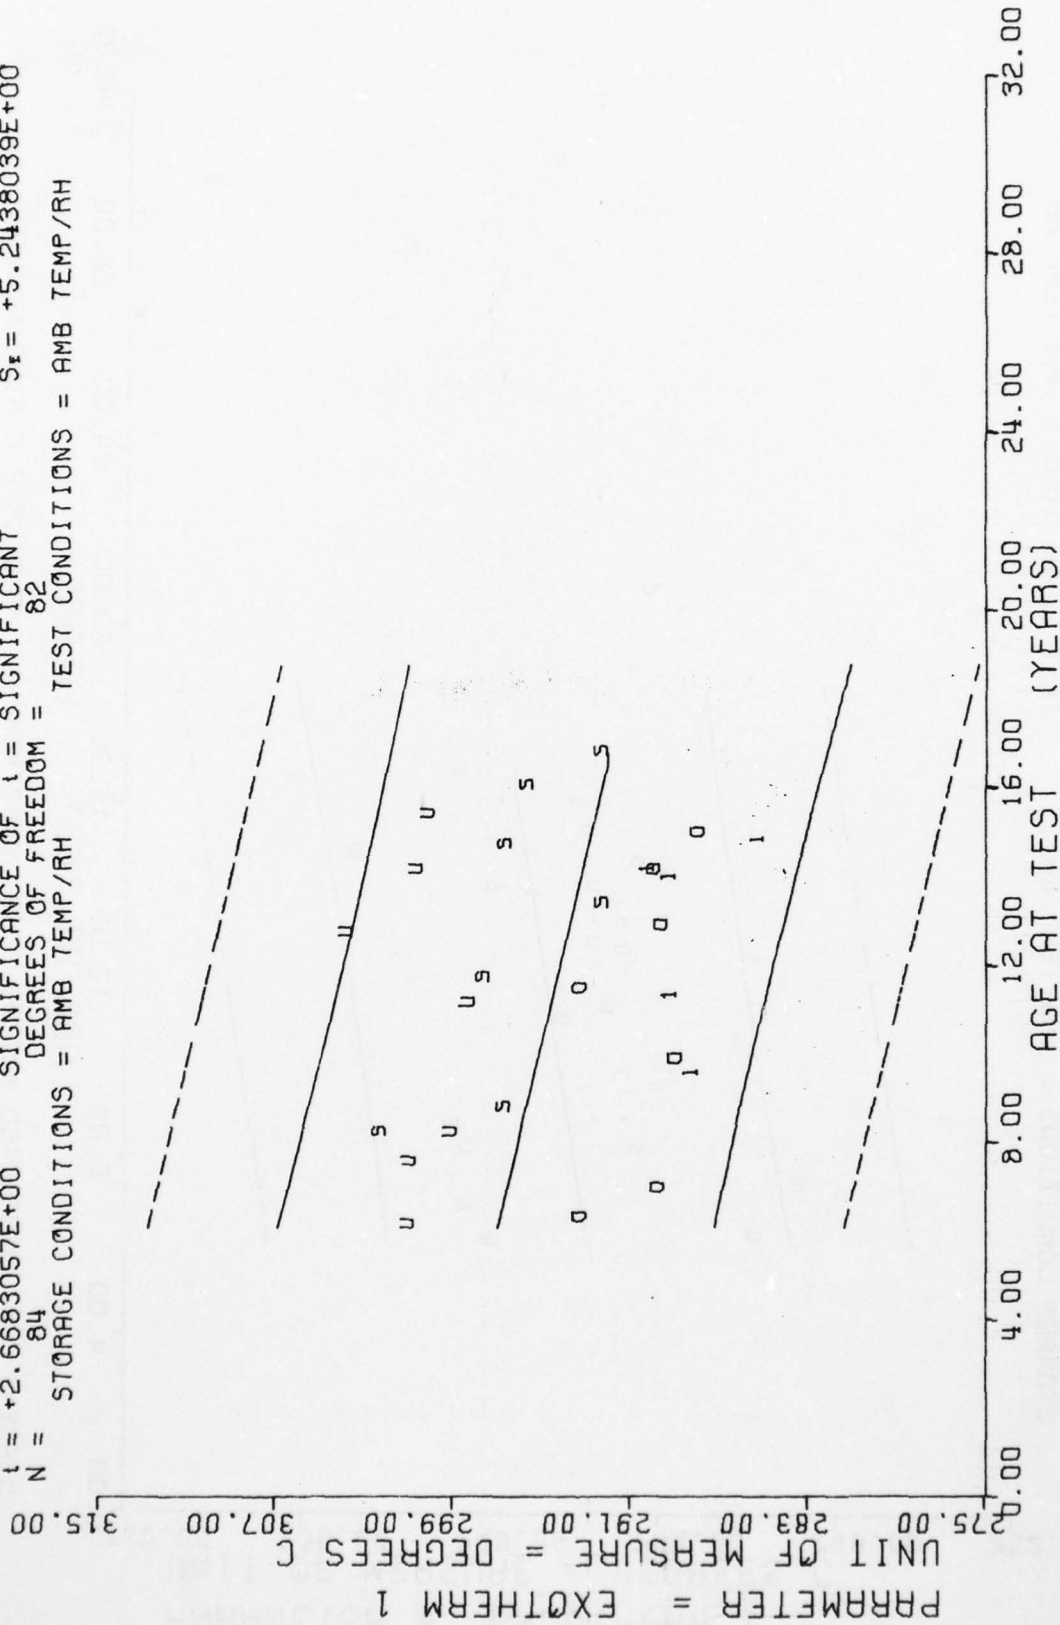

STAGE 1 DISSECTED MOTORS, DTA, EXOTHERM 1, 12 DEGREE C RISE/MINUTE

Figure 45

*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
73.0	4
75.0	3
83.0	2
90.0	3
98.0	3
105.0	5
114.0	2
133.0	3
135.0	2
140.0	3
152.0	2
154.0	1
167.0	2
169.0	6
176.0	2
177.0	3
179.0	2
184.0	5
192.0	3
201.0	3

STAGE 1 DISSECTED MOTORS, DTA IGNITION TEMP, 12 DEG C RISE/MINUTE


This sample size summary is applicable to figure 46.

$F = +1.2835442E+01$
 $R = +4.1140475E-01$
 $t = +3.5826585E+00$
 $N = 65$

$Y = ((+3.5261042E+02) + (+1.0680296E-01) * X)$

SIGNIFICANCE OF F = SIGNIFICANT $\sigma_1 = +1.0893121E+01$
 SIGNIFICANCE OF R = SIGNIFICANT $S_1 = +2.9811091E-02$
 SIGNIFICANCE OF t = SIGNIFICANT $S_t = +1.0007053E+01$

DEGREES OF FREEDOM = 63
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

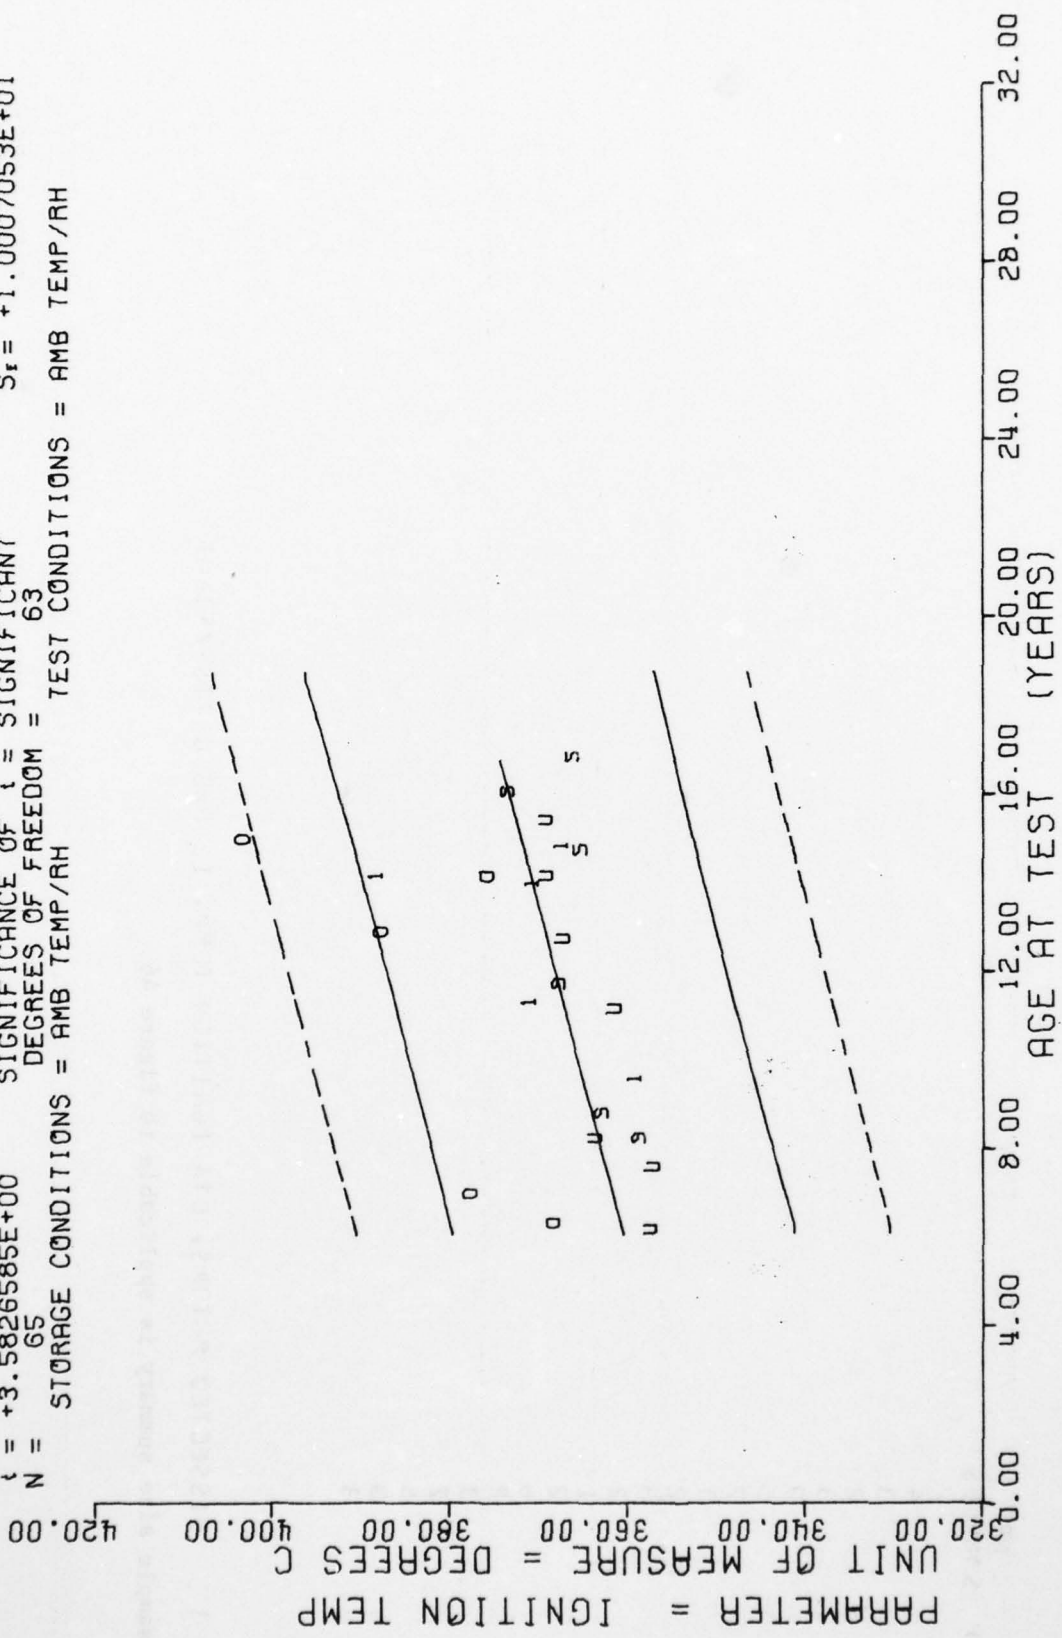

STAGE 1 DISSECTED MOTORS, DTA IGNITION TEMP, 12 DEG C RISE/MINUTE

Figure 46


*** SAMPLE SIZE SUMMARY ***

AGE (MONTHS)	NR SAMPLES
133.C	4
135.C	4
146.C	4
148.C	4
150.C	4
152.C	4
154.C	4
157.C	4
163.C	4
167.C	6
169.C	4
170.C	4
175.C	4
184.C	6
191.C	6

DISSECTED MTR, STAGE 1, IP-HIC11, SOL GEL, PERCENT EXTRACTABLES

This sample size summary is applicable to figures 47 thru 50.


$Y = ((+8.0798083E+00) + (-6.2924187E-03) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT $S_f = +3.9922579E-01$
 SIGNIFICANCE OF R = SIGNIFICANT $S_r = +2.8311394E-03$
 SIGNIFICANCE OF χ^2 = SIGNIFICANT $S_{\chi^2} = +3.8765031E-01$
 DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

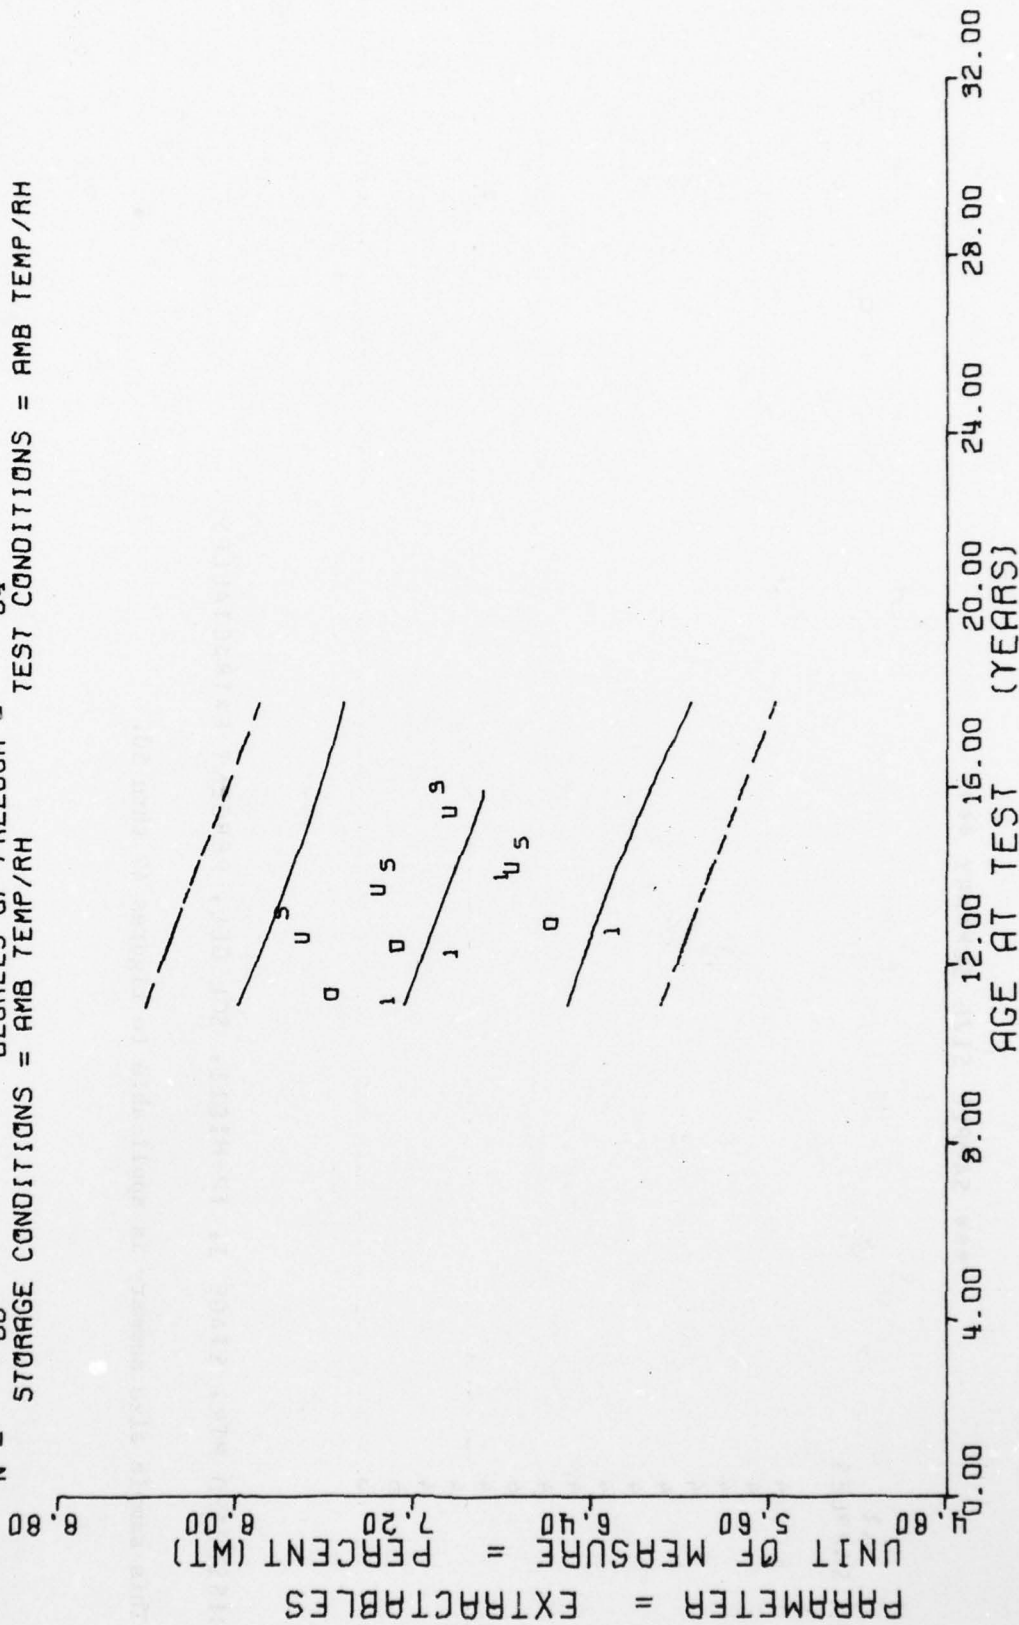

DISSECTED MTR, STAGE 1, TP-H1011, SOL GEL, PERCENT EXTRACTABLES

Figure 47


$Y = ((+4.1348895E+00) + (-2.8076343E-03) * X)$
 F = +4.8216692E+00 SIGNIFICANCE OF F = SIGNIFICANT $\sigma_f = +1.8014683E-01$
 R = -2.6468912E-01 SIGNIFICANCE OF R = SIGNIFICANT $S_e = +1.2786210E-03$
 t = +2.1958299E+00 SIGNIFICANCE OF t = SIGNIFICANT $S_e = +1.7507362E-01$
 N = 66 DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH TEST CONDITIONS = AMB TEMP/RH

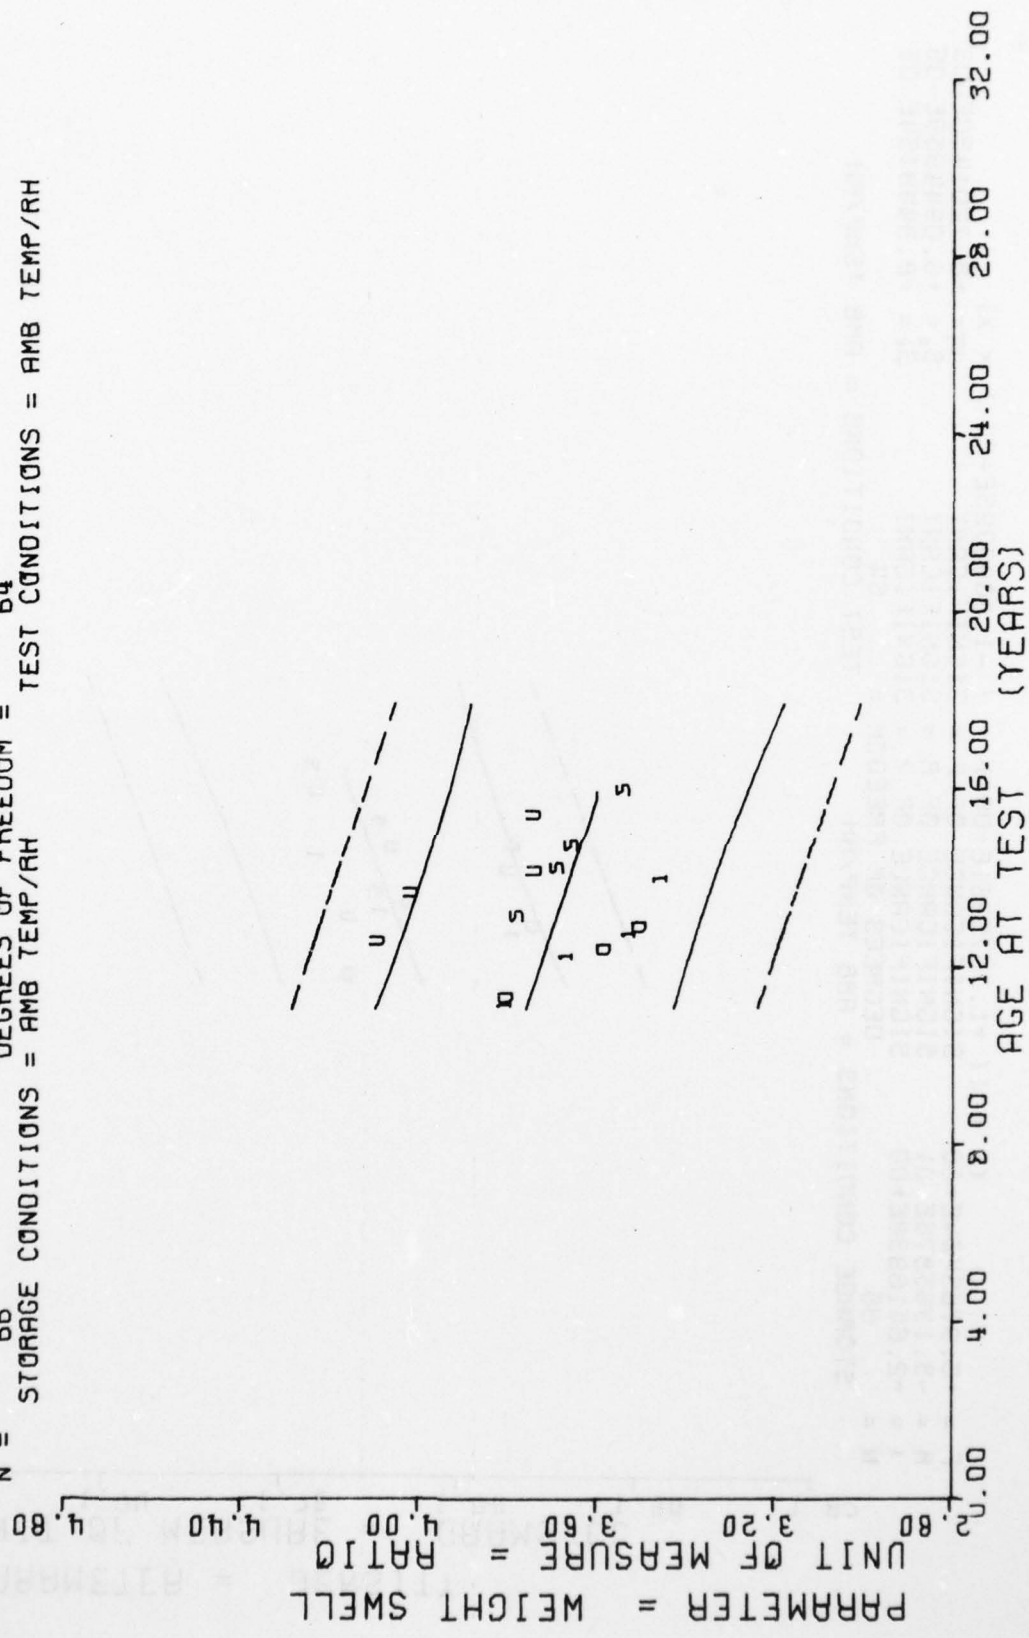

DISSECTED MTA, STAGE 1, TP-H1011, SOL GEL, WT SWELL RATIO

Figure 48

$Y = ((+1.7975951E+00) + (-1.6099795E-04) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT $\sigma_1 = +8.7201430E-03$
 SIGNIFICANCE OF R = SIGNIFICANT $S_0 = +6.0944969E-05$
 SIGNIFICANCE OF t = SIGNIFICANT $S_1 = +8.3448154E-03$
 DEGREES OF FREEDOM = 64
 STORAGE CONDITIONS = AMB TEMP/RH
 TEST CONDITIONS = AMB TEMP/RH

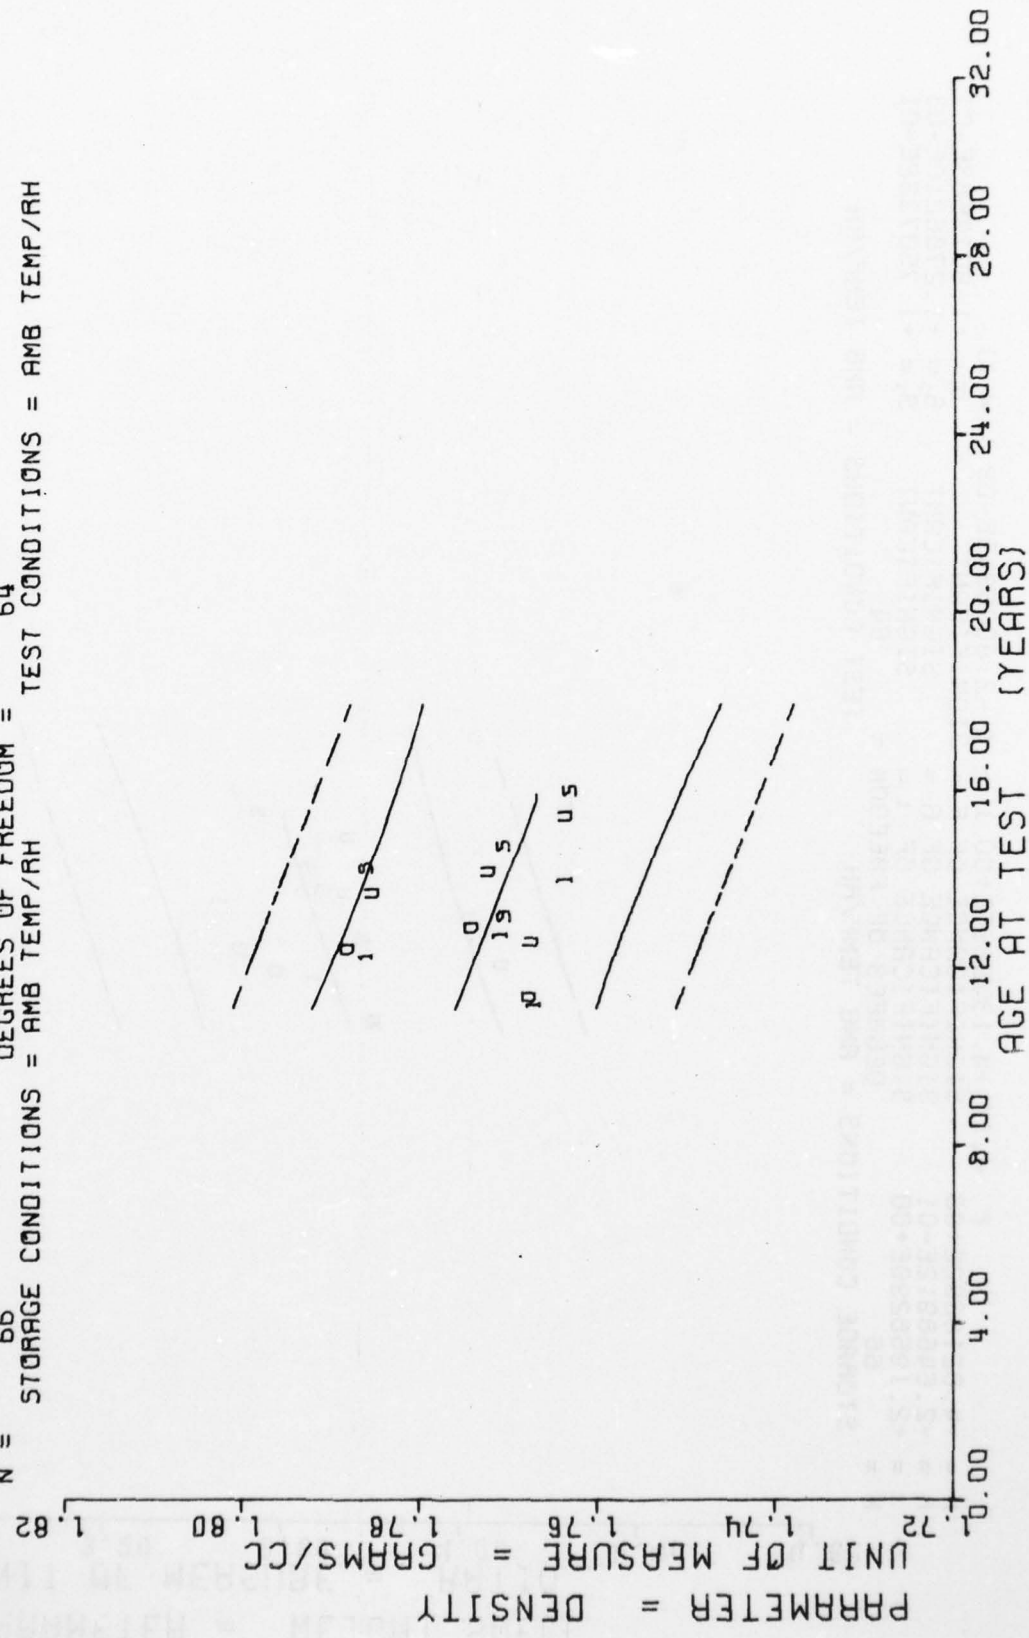

DISSECTED MTR, STAGE 1, TP-H1011, SOL GEL, DENSITY

Figure 49

$F = +1.0159758E+01$
 $R = -3.7013277E-01$
 $t = +3.1874376E+00$
 $N = 66$

$Y = ((+1.6561716E-02) + (-3.7854115E-05) * X)$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 64

STORAGE CONDITIONS = AMB TEMP/AH TEST CONDITIONS = AMB TEMP/AH


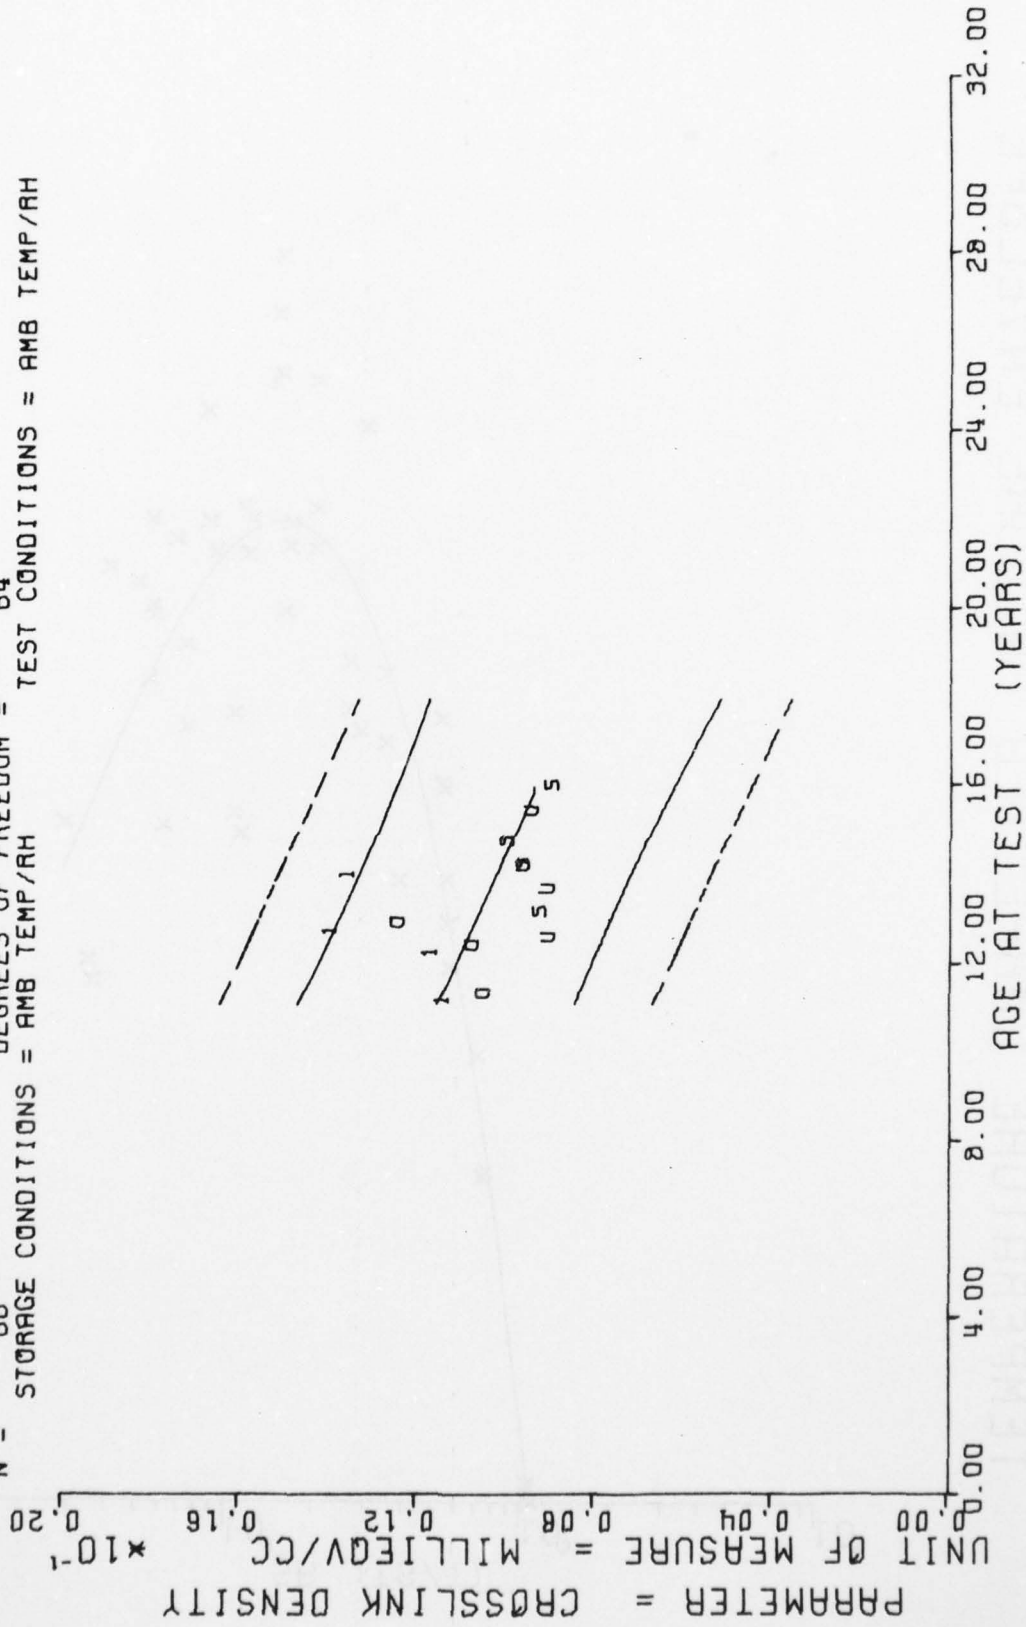


Figure 50

TEMPERATURE CORRECTED FAILURE ENVELOPE

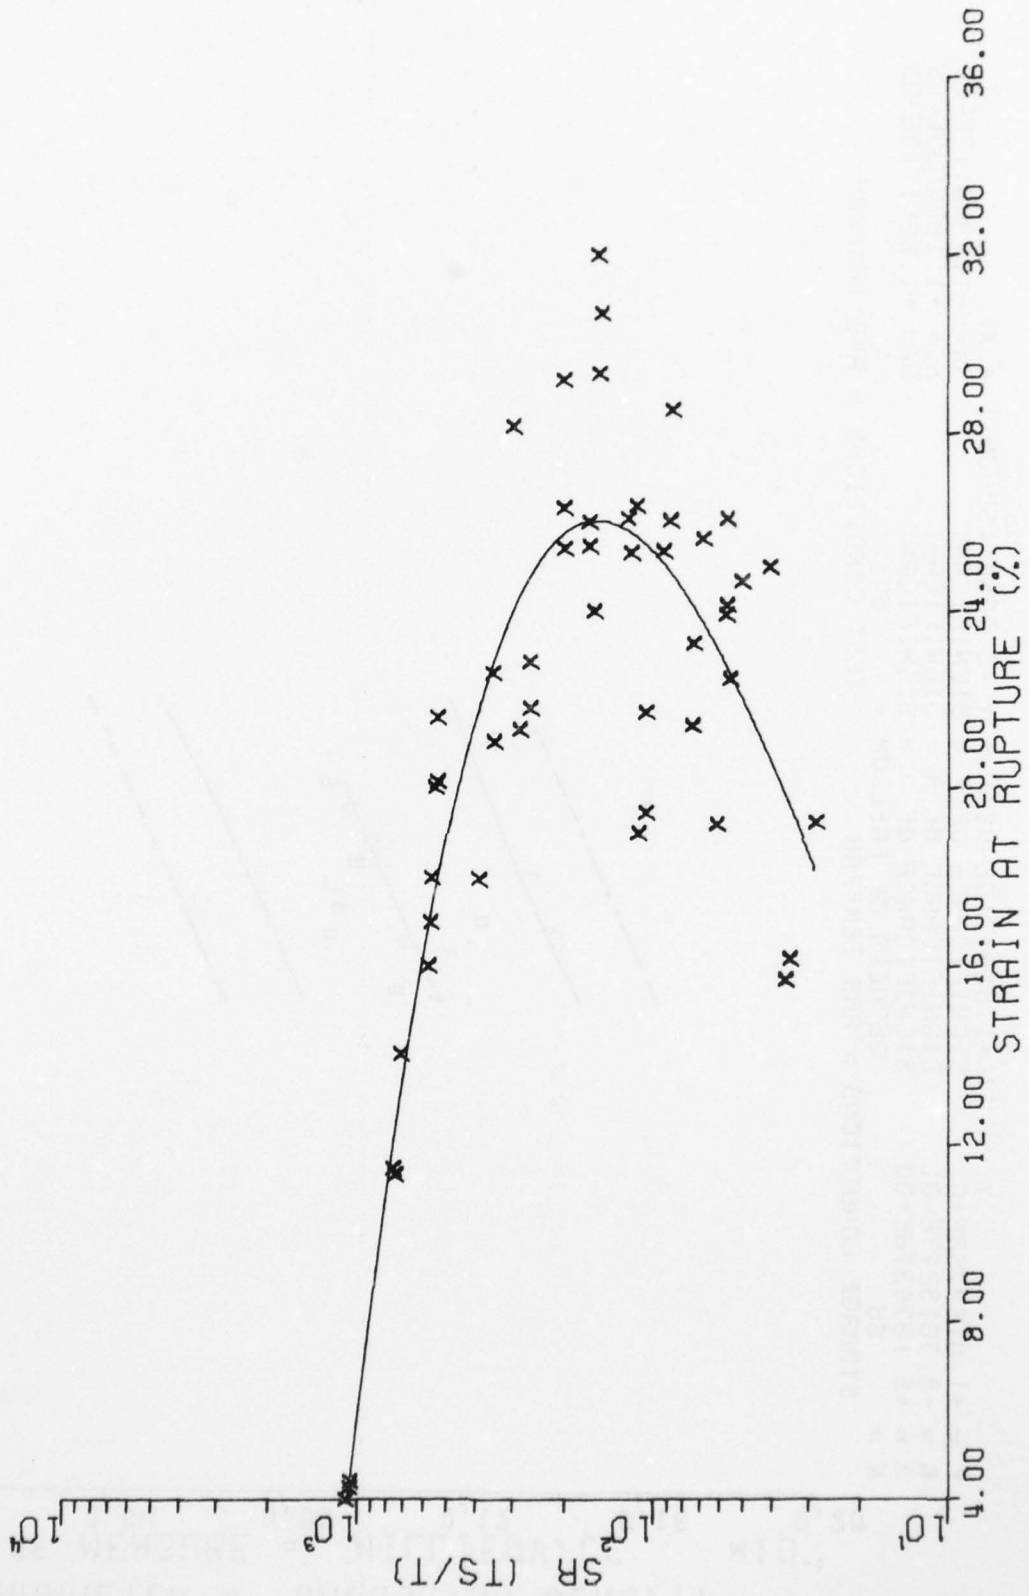

FAILURE ENVELOPE (MOTOR/SN 0012099) DISSECTED MOTOR, STAGE I, TP-H1011

Figure 51

DISTRIBUTION

	NR <u>COPIES</u>
OOALC	
MMWRME	1
MMWRMT	1
DDC (TISIR) Cameron Station, Alexandria, VA 22314	2
AFPRO, Thiokol Chemical Corporation	2
Wasatch Division	
P.O Box 524	
Brigham City, Utah 84302	
(Cy to R. E. Keating)	
AFRPL (MKPB) Edwards AFB, CA 93523	1
SAC (LGMB) Offutt AFB, NB 68113	1
U. S. Naval Ordnance Station, Indian Head, MD 20640	1
Attn: Dr. James H. Wiegand	
Fleet Support Dept., Propulsion	
System Development Division, Code F37	
CPIA, Applied Physics Laboratory	1
John Hopkins University	
John Hopkins Road	
Laurel, MD 20810	
Attn: Dr. P.L. Nichols	
Naval Plant Branch Representative	1
Attn: Mr. David W. Pratt	
P.O. Box 157	
Bacchus Works	
Magna, Utah 84044	

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 406 (78)	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Minuteman Stage I Dissected Motor Program		5. TYPE OF REPORT & PERIOD COVERED Test Results - Semi Annual
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) John A. Thompson		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Propellant Lab Section Directorate of Maintenance 00-ALC Hill AFB, UT 84406		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS MMWRM Project M82934C- WNL 17514
11. CONTROLLING OFFICE NAME AND ADDRESS Service Engineering Division Directorate of Materiel Management 00-ALC Hill AFB, UT 84406		12. REPORT DATE November 1978
		13. NUMBER OF PAGES 97
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release, Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Minuteman Solid Propellant		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Testing was performed to determine the useful shelf/service life for LGM-30 Stage I Rocket Motors. A three year storage program for propellant and components was started in May 1961. This program was then extended to a ten year study and later continued indefinitely to assure that a deterioration in motor physical characteristics could be detected in time to take some corrective actions before the weapon system performance deteriorated below an acceptable level. →		

(over)

AD-A063 122

OGDEN AIR LOGISTICS CENTER HILL AFB UTAH PROPELLANT L--ETC F/G 21/9.2
SURVEILLANCE REPORT. STAGE I DISSECTED MOTORS. PHASE X. PROPELL--ETC(U)
NOV 78 J A THOMPSON

UNCLASSIFIED


MANCP-406(74)

NL

2 OF 2
AD
A063 122



END
DATE
FILMED
3-79
DDC

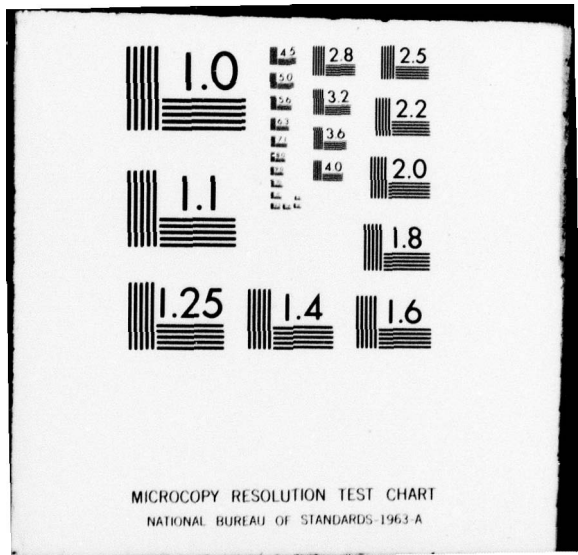

→ This report covers only propellant data and limited case bond data. The malfunction of an environmental chamber destroyed component samples that had originally been part of this testing program (and the inadvertent burning of some motors during dissection reduced the material available for testing). Planned dissection of selected motors in the future will provide samples for continued component testing. Test specimens for this reporting period were obtained from motors STM-012, 0012099, 0012199 and UP-7775 block propellant.

Separate analyses were made on the respective motors and block propellant for the second time in this report and are shown in the regressions. The plotting symbols for each motor and block propellant are listed in the statistical analyses section.

The data from this test period was combined with data from previous testing and entered into the G085 computer for storage, analysis, and regression analysis. From the statistical analysis of all data tested to date, significant degradation of the propellant does not appear likely for at least two years past the oldest data point. ←

Future testing will be conducted on dissected motors.