

AD-A068 029


FOREST PRODUCTS LAB MADISON WIS  
WOOD ANATOMY OF THE NEOTROPICAL SAPOTACEAE. I. 'BUMELIA'.(U)  
1978 B F KUKACHKA  
FSRP-FPL-325

F/6 2/6

UNCLASSIFIED

NL

| OF |  
AD  
A068029

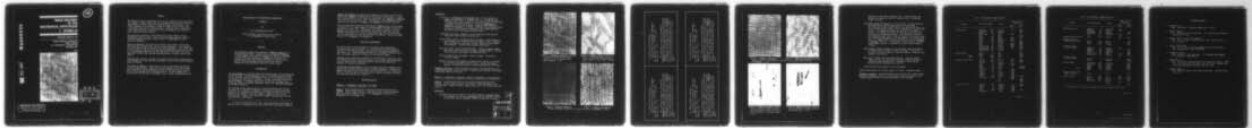

END  
DATE  
FILMED  
6-79  
DDC


12

**WOOD ANATOMY  
OF THE  
NEOTROPICAL SAPOTACEAE  
I. BUMELIA**

*RESEARCH PAPER FPL 325*

*FOREST PRODUCTS LABORATORY  
FOREST SERVICE  
U.S. DEPARTMENT OF AGRICULTURE  
MADISON, WIS.*

1978

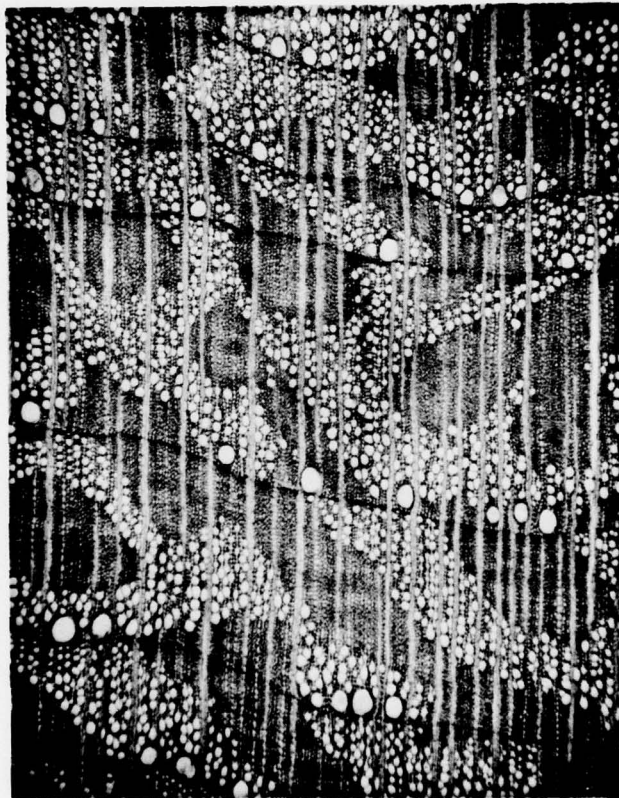

AD A 068029

DDC FILE COPY

DDC  
RECEIVED  
MAY 2 1979  
B

**DISTRIBUTION STATEMENT A**  
Approved for public release;  
Distribution Unlimited

79 04 25 118

## Preface

The Sapotaceae form an important part of the ecosystem in the neotropics; for example, limited inventories in the Amazon Basin indicate that this family makes up about 25% of the standing timber volume there. This would represent an astronomical volume of timber but at present only a very small fraction is being utilized. Obviously better information would help utilization--especially if that information can result in clear identification of species.

The Sapotaceae represent a well-marked and natural family but the homogeneous nature of their floral characters makes generic identification extremely difficult. This in turn is responsible for the extensive synonymy.

Baehni and Bernardi (3) state the situation with respect to Peru but this would hold equally well for all of the neotropics: "For instance, of the 39 species and one variety described hereunder, 13 are known only from the Peruvian type; and 23 taxa here presented have no fruit or seed. It is universally admitted that the taxonomy of this family is almost impossible without--for the same species--leaves, flowers, fruits, and seeds."

Unfortunately, species continue to be named on the basis of flowering or fruiting material alone and this continues to add to the already confused state of affairs.

This paper on Bumelia is the first of a series describing the anatomy of the secondary xylem. Publication in this manner will afford interested anatomists and taxonomists the time to make known their opinions and all such information is hereby solicited. At the termination of this series the data will be assembled into a single comprehensive unit.

(6) WOOD ANATOMY OF THE NEOTROPICAL SAPOTACEAE  
I. BUMELIA

11 1978

By

(10) B. F. Kukachka / Botanist<sup>1/</sup>

(12) 11 p. r

Forest Products Laboratory, Forest Service  
U.S. Department of Agriculture

(14) FSRP-FPL-325

(9) Forest Service  
research paper

Abstract

Two anatomical groups are recognized in Bumelia; Bumelia A is characterized by small, angular pores and tracheids arranged in flame-shaped tracts and the presence of spiral thickenings in the vessels and tracheids; in Bumelia B the pores are rounded in outline and arranged in radial or echelon tracts and the axial parenchyma has scattered cells that are completely filled with microcrystals (crystal sand).

Introduction

The genus Bumelia is the most widely distributed genus of the Sapotaceae in the Americas. The northernmost limit is in Central Missouri, about 39° N. latitude, and the southernmost limit is in Corrientes Province of Argentina at about 30° S. latitude. In habit the genus varies from small decumbent or ascending shrubs and small trees to large trees producing timber of economic importance, such as B. obtusifolia excelsa of northern Argentina.

The taxonomy of the species native to the United States was covered by Clark (4) in which he recognized 14 species and several varieties. Cronquist (5) recognized 23 species and a number of varieties in the Americas but reduced to five the number of species native to the United States. Eight of his species are known from type only or from less than five collections.

1/ Pioneering Research Unit, FPL. The Laboratory is maintained at Madison, Wis. in cooperation with the University of Wisconsin, Madison.

141 700  
79 04 25  
Jm  
118

Bumelia and Dipholis are generally recognized as distinct taxa but were united under Bumelia by Baehni (2) in his survey of the family. In the most recent treatise on the family by Aubréville (1), Bumelia and Dipholis were considered as distinct taxa. The anatomy of the secondary xylem supports the separation of Bumelia and Dipholis as distinct entities.

The last published anatomical description of Bumelia was a brief account by Record (7) of a small number of wood specimens available in the Yale Collection at that time. Taxonomists have made no attempt to divide Bumelia into sections but the present description takes into account the fact that there are two basic anatomical types and the differences are of a magnitude that warrant separate descriptions. These are simply referred to as Bumelia A and Bumelia B.

#### Materials and Methods

For this study 73 wood specimens were examined which represented 11 species and varieties (table 1). Microscope slides were prepared from all of the wood specimens using the new techniques developed by the author (6). These techniques resulted in successful slides on wood that was almost impossible to handle by conventional means.

Although a few slides were available in the Laboratory collection, they were eliminated from contention because it was evident that hydrofluoric acid had been used for softening and this effectively removed all evidence of crystalline material.

Terminology and measurements are in accordance with the standards developed by the International Association of Wood Anatomists. Photomicrographs were made with a Zeiss camera utilizing Polaroid 4 X 5 Land film type 55. Specific gravity values cited are based on weight and volume at a moisture content of 6-7 percent.

#### Wood Description

##### Bumelia A. (lanuginosa, lycioides, and tenax)

General: Wood yellowish with no distinction between heartwood and sapwood. Growth rings distinct. Wood hard, heavy, and fine-textured. Specific gravity range of 0.54 to 0.85 (lanuginosa average 0.73; lycioides 0.74; and tenax 0.76).

Anatomical:

Arc-porous in lanuginosa and lycioides (fig. 1) but variable in tenax from arc-porous to diffuse (fig. 2). Earlywood pores solitary and in short uniseriate arcs; mostly oval and attaining a maximum tangential diameter of 118  $\mu\text{m}$  in lanuginosa and lycioides; up to 80  $\mu\text{m}$  in tenax. Latewood pores angular in outline and embedded in vascular tracheids, which together form distinctive flame-shaped or dendritic tracts emanating from the short arcs of the large earlywood pores.

Parenchyma reticulate, diffuse, and also forming closely spaced uniseriate lines between the wood rays.

Vessel members short, averaging 350  $\mu\text{m}$  in length. Inter-vessel or more commonly the vessel-tracheid pit pairs 6-8  $\mu\text{m}$  in diameter. Spirals present to a greater or lesser degree in the vessels and tracheids. Tyloses, when present, thin-walled.

Wood rays (1)2-4 seriate, heterocellular. Vertical fusions common. The normal rays (unfused) attaining a maximum height of 375  $\mu\text{m}$ . Vessel-ray pitting irregular in shape and size.

Fibers thick-walled; averaging 1.24 mm in length. Vascentric tracheids common.

Rhombic crystals, microcrystals (crystal sand), and silica lacking in the axial parenchyma and wood rays. Pale brown organic deposits occasionally present in the parenchyma and wood rays.

Diagnostic features: Wood yellowish; arc-porous, the latewood pores in flame-shaped tracts; spirals present in vessels and tracheids; and without crystalline deposits or silica.

Bumelia B. (celastrina, glomerata, obovata, obtusifolia, and persimilis)

General: Wood yellowish with no distinction between heartwood and sapwood. Growth rings indistinct or lacking. Wood hard, heavy, and fine-textured. Specific gravity ranges from 0.75 to 1.07 with an average of 0.87.

Anatomical:

Diffuse-porous; pores round or oval and attaining a maximum tangential diameter of 142  $\mu\text{m}$  in persimilis but not exceeding 110  $\mu\text{m}$  in the other species examined. Pores solitary and in radial

the Section   
Section

|            |                                 |                |
|------------|---------------------------------|----------------|
| PER LETTER |                                 |                |
| BY         | DISTRIBUTION/AVAILABILITY CODES |                |
| Dist.      | AVAIL.                          | and/or SPECIAL |
| A          |                                 |                |

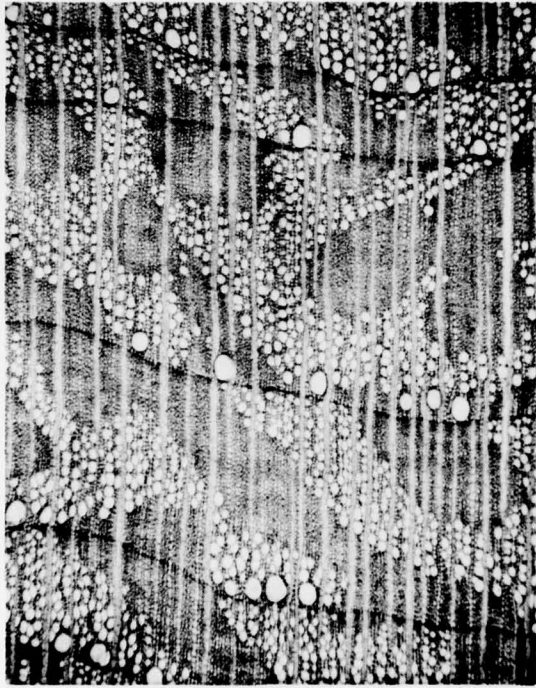


Figure 1.--Bumelia lanuginosa, showing arc-porous condition and flame-shaped tracts of latewood pores and tracheids. X 30.

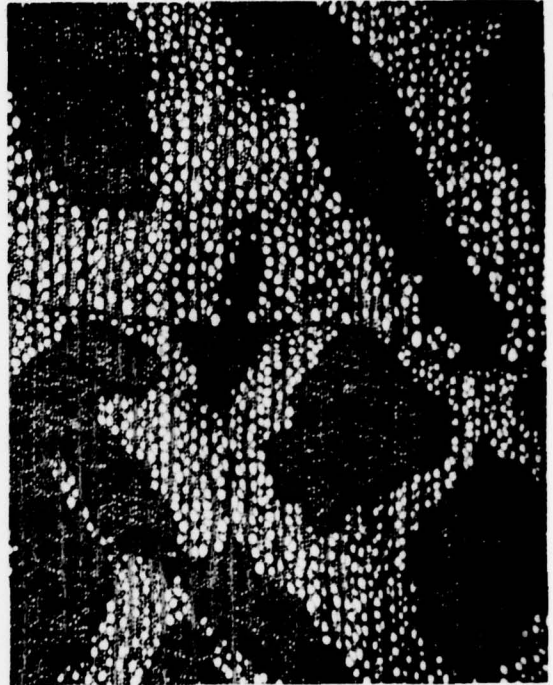


Figure 2.--Bumelia tenax, similar to figure 1 but with earlywood pores only slightly larger than latewood. X 30.

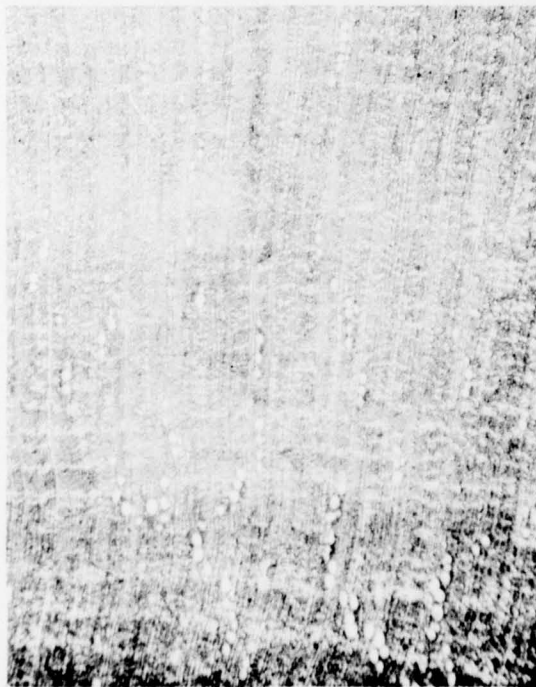


Figure 3.--Bumelia glomerata. Compare extremes of pore size in radial-echelon arrangement. X 30.

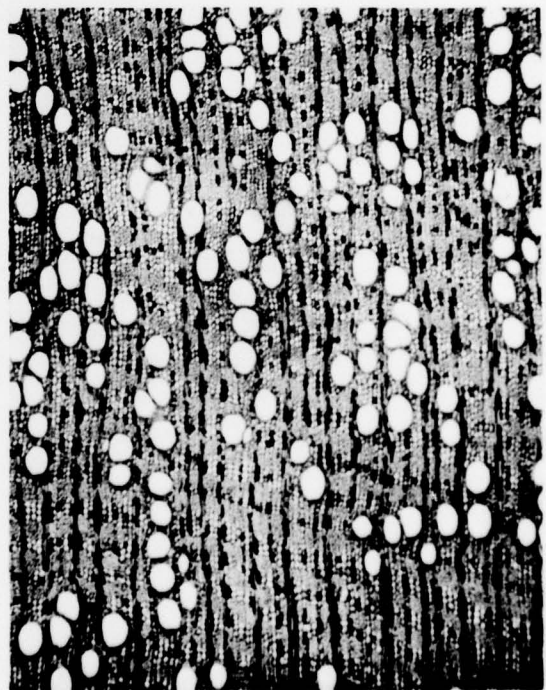


Figure 4.--Bumelia panamensis.

U.S. Forest Products Laboratory.

Wood anatomy of neotropical Sapotaceae:

- I. Bumelia, by B. F. Kukachka. Res. Pap. FPL 325, For. Serv., U.S. Dep. Agr., Madison, Wis. 9 p.

Two anatomical groups are recognized:

Bumelia A has small, angular pores and tracheids arranged in flower-shaped tracts and with spiral thickenings in vessels and tracheids. Bumelia B has rounded pores arranged in radial or echelon tracts. Axial parenchyma has scattered cells completely filled with microcrystals (crystal sand).

U.S. Forest Products Laboratory.

Wood anatomy of neotropical Sapotaceae:

- I. Bumelia, by B. F. Kukachka. Res. Pap. FPL 325, For. Serv., U.S. Dep. Agr., Madison, Wis. 9 p.

Two anatomical groups are recognized:

Bumelia A has small, angular pores and tracheids arranged in flower-shaped tracts and with spiral thickenings in vessels and tracheids. Bumelia B has rounded pores arranged in radial or echelon tracts. Axial parenchyma has scattered cells completely filled with microcrystals (crystal sand).

U.S. Forest Products Laboratory.

Wood anatomy of neotropical Sapotaceae:

- I. Bumelia, by B. F. Kukachka. Res. Pap. FPL 325, For. Serv., U.S. Dep. Agr., Madison, Wis. 9 p.

Two anatomical groups are recognized:

Bumelia A has small, angular pores and tracheids arranged in flower-shaped tracts and with spiral thickenings in vessels and tracheids. Bumelia B has rounded pores arranged in radial or echelon tracts. Axial parenchyma has scattered cells completely filled with microcrystals (crystal sand).

U.S. Forest Products Laboratory.

Wood anatomy of neotropical Sapotaceae:

- I. Bumelia, by B. F. Kukachka. Res. Pap. FPL 325, For. Serv., U.S. Dep. Agr., Madison, Wis. 9 p.

Two anatomical groups are recognized:

Bumelia A has small, angular pores and tracheids arranged in flower-shaped tracts and with spiral thickenings in vessels and tracheids. Bumelia B has rounded pores arranged in radial or echelon tracts. Axial parenchyma has scattered cells completely filled with microcrystals (crystal sand).

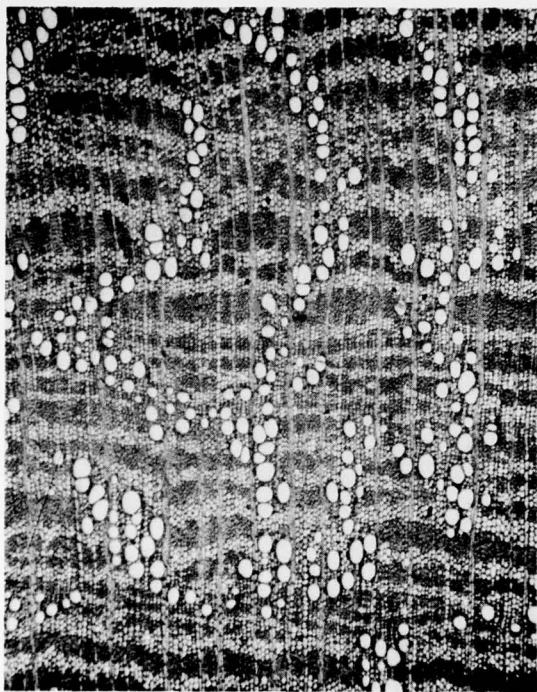


Figure 5.--*Bumelia celastrina*.

Compare pores of intermediate size and in clustered radial-echelon arrangement. X 30.

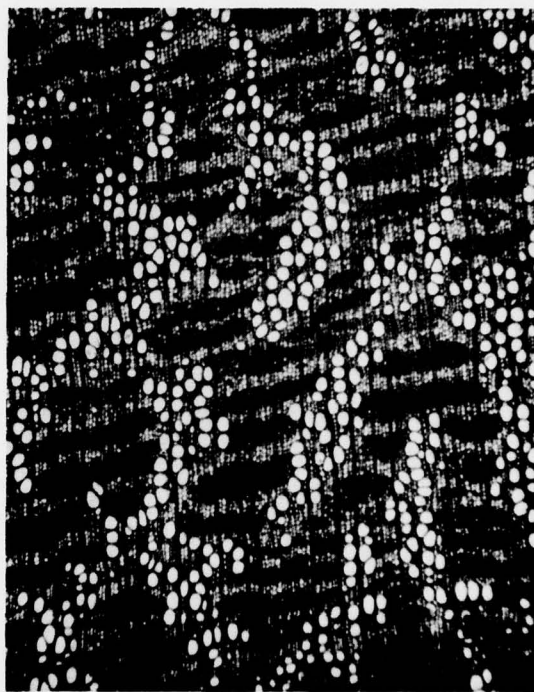


Figure 6.--*Bumelia obtusifolia excelsa*.



Figure 7.--*Bumelia obovata*, showing normal crystal strands and three axial parenchyma cells filled with micro-crystals. Polarized light. X 275.



Figure 8.--*Bumelia obovata*, showing two strands of two-sized crystals. Polarized light. X 275.

multiples to five (most commonly 2-3). Solitary pores and multiples arranged in radial or echelon files or groupings (figs. 3,4,5,6).

Parenchyma banded and generally 3 to 5 seriate. In some instances the bands may be loosely aggregated or discontinuous. Microcrystals always present in the axial parenchyma (fig. 7); cells containing the crystals few to abundant in a given radial section. In comparing freshly cut sections with finished slides it is evident that many of these may be "washed" away during the slide-making procedure. The individual crystals are extremely small (up to 2  $\mu\text{m}$ ) and consist of calcium oxalate. The crystalline aggregates are birefringent in polarized light (fig. 7). Rhombic and two-sized crystals present in glomerata and obovata (fig. 8). In two-sized crystals usually a single, large rhombic crystal is embedded in a mass of much smaller crystals.

Vessel-member length averages for all specimens range from 350  $\mu\text{m}$  to 560  $\mu\text{m}$  with an overall average of 456  $\mu\text{m}$ . Inter-vessel pit-pairs 4-6  $\mu\text{m}$  in diameter. Spirals lacking. Tyloses, when present, thin walled.

Wood rays (1)2-4(5) seriate; heterocellular. Vertical fusions common; normal rays (unfused) attaining a maximum height of 670  $\mu\text{m}$  but most commonly with a maximum of about 500  $\mu\text{m}$ . Without crystalline deposits or silica.

Vessel-ray pitting irregular in size and shape.

Fibers thick-walled; an average length of 1.38 mm. Tracheids common.

Diagnostic features: Wood yellowish; pores solitary and in short radial multiples arranged in radial or echelon files; spirals lacking; microcrystals always present in axial parenchyma; silica lacking.

Table 1.--Wood specimens of *Bumelia* examined

| Species                          | Collector and number | Origin    | Numbers in wood collection |          |
|----------------------------------|----------------------|-----------|----------------------------|----------|
|                                  |                      |           | MADw                       | SJRw*    |
| <i>celastrina</i> H.B.K.         | Caldwell 8783        | Florida   | 4122                       | 49310    |
|                                  | Curran-Haman 534     | Venezuela |                            | 2827     |
|                                  | Dugand 231           | Colombia  |                            | 22520    |
|                                  | Field Museum sn      | U.S.      | 24964                      |          |
|                                  | Mell 3               | Mexico    |                            | 6981     |
|                                  | Nogle 330            | Texas     |                            | 42538    |
|                                  | Ortega 52            | Mexico    | 32856                      | 1211     |
|                                  | Pittier 4988         | Panama    | 5817                       |          |
|                                  | Record 123           | Guatemala | 32878                      | 10074    |
|                                  | Scott sn             | Florida   |                            | 36371    |
|                                  | Stern 85             | Florida   | 16879                      | 49428    |
|                                  | Stern 117            | Florida   | 32860                      | 49443    |
|                                  | Stern-Brizicky 293   | Florida   | 18245                      | 51123    |
|                                  | Stern-Brizicky 322   | Florida   | 18251                      | 51146    |
|                                  | Stern-Brizicky 355   | Florida   |                            | 51171    |
|                                  | Stern-Brizicky 452   | Florida   |                            | 51235    |
| <i>glomerata</i> Griseb.         | Bucher sn            | Cuba      |                            | 16137    |
|                                  | Bucher 66            | Cuba      |                            | 16239    |
|                                  | (stem) Acuna 16467   | Cuba      |                            | 40732    |
|                                  | (root) Acuna 16467   | Cuba      |                            | 40733    |
| <i>lanuginosa</i> (Michx.) Pers. | Beilmann 8507        | Missouri  | 9432                       | 49049    |
|                                  | Bur. For. 1615       | U.S.      | 32872                      | 11840    |
|                                  | Detweiler 48         | Arizona   |                            | 14773    |
|                                  | King sn              | Oklahoma  | 20027                      |          |
|                                  | Nogle 234            | Texas     | 13220                      |          |
|                                  | Palmer sn            | Texas     |                            | 22801(H) |
|                                  | Palmer 33973         | Texas     |                            | 20996(H) |
|                                  | Phil. Expo. 4        | U.S.      | 2864                       |          |
|                                  | Sackett sn           | U.S.      | 2957                       |          |
|                                  | Stearns 521          | Texas     | 9646                       |          |
|                                  | Sudworth 1           | Arizona   | 2955                       |          |
|                                  | Sudworth 2           | Arizona   | 2956                       |          |
|                                  | Tharp 8269           | Texas     | 8981                       | 49048    |
|                                  | 10th Census 139      | U.S.      | 20444                      |          |
|                                  |                      | U.S.      | 32861                      | 6695     |
|                                  | U.S.                 |           | 21841                      |          |
|                                  | U.S.                 |           | 11842                      |          |
| <i>lycioides</i> (L.) Pers.      | Anderson 94          | Florida   |                            | 45883    |
|                                  | Bur. For. 1616       | Tennessee | 32876                      | 11843    |
|                                  | Harper 1             | Georgia   | 2968                       |          |
|                                  | Koehler 108          | Missouri  | 2948                       |          |
|                                  | Nogle 2600           | Texas     | 13264                      | 47416    |
|                                  | Nogle-Wilson 8       | Texas     | 15586                      |          |

(Page 1 of 2)

Table 1.--Wood specimens of *Bumelia* examined--con.

| Species  | Collector and number |         | Origin      | Numbers in wood collection |          |
|--|----------------------|---------|-------------|----------------------------|----------|
|  |                      |         |             | MADw                       | SJRw*    |
| <i>obovata</i> (Lam.) A. DC.                             | Commercial           | sn      | Puerto Rico | 3594                       |          |
|  | Commercial           | 141     | Venezuela   | 3615                       |          |
|  | Curran-Haman         | 158     | Curacao     |                            | 2137     |
|  | Curran-Haman         | 410     | Venezuela   |                            | 2785     |
|  | Miller               | 1631    | Puerto Rico | 20858                      |          |
| <i>obtusifolia</i> Roem. and Schult.                     | Little               | 6612    | Ecuador     | 10427                      | 40978    |
| <i>Obtusifolia buxifolia</i><br>(Roem. and Schult.) Miq. | Curran               | 524     | Curacao     |                            | 2820     |
|  | Judd                 | 3620    | Hawaii      |                            | 37272    |
|  | Pittier              | 12432   | Venezuela   |                            | 11067    |
| <i>obtusifolia excelsa</i><br>(A. DC.) Cronquist         | Commercial           | sn      | Paraguay    | 1025                       |          |
|  | Commercial           | 109     | Argentina   |                            | 6253     |
|  | Commercial           | 1619    | Argentina   |                            | 3974     |
|  | Curran               | 378     | Argentina   |                            | 1044     |
|  | Forest Service       | 33      | Brazil      | 13106                      | 36098    |
|  | Forest Service       | 313     | Argentina   | 12164                      | 23539    |
| <i>obtusifolia excelsa</i><br>(A. DC.) Cronquist         | Noverras             | 9       | Argentina   |                            | 14966    |
|  | Venturi              | 1       | Argentina   |                            | 22802(H) |
| <i>persimilis</i> Hemsl.<br><br>(root)                   | Austin Smith         | 4163    | Costa Rica  |                            | 38379    |
|  | Austin Smith         | 4229    | Costa Rica  |                            | 38440    |
|  | Dugand               | 508     | Colombia    |                            | 27080    |
|  | Dugand               | 823     | Colombia    |                            | 29653    |
|  | Dugand               | 849     | Colombia    |                            | 29679    |
|  | Kluge                | 12      | Panama      |                            | 7126     |
| <i>persimilis subsessiliflora</i><br>(Hemsl.) Cronquist  | Ortega               | sn      | Mexico      |                            | 10387    |
| <i>tenax</i> (L.) Willd.                                 | Bur. For.            | 1614    | U.S.        | 32877                      | 11844    |
|  | Rhoads               | 8397    | Florida     | 9356                       | 49050    |
|  | Smith, H. H.         | 74889   | Georgia     | 32859                      | 26936    |
|  | 10th Census          | 178     | Florida     |                            | 5181     |
|  |                      |         | U.S.        | 2967                       |          |
|  |                      | Florida |             | 6694                       |          |

\* Specimen numbers in the right column marked (H) are from the Harvard Wood Collection.

(Page 2 of 2)

Literature Cited

1. Aubréville, A.  
1964. Sapotacées. *Adansonia Mémoire* No. 1:1-157.
2. Baehni, Charles.  
1965. Mémoires sur les Sapotacées. III. Inventaire des genres. *Boissiera* II:1-262.
3. Baehni, Charles, and Luciano Bernardi.  
1970. Flora of Peru. *Field Mus. Nat. Hist.* XIII:Part V-A, No. 3:135-177.
4. Clark, Robert Brown.  
1942. A revision of the genus Bumelia in the United States. *Ann. Missouri Bot. Gard.* 29:155-182.
5. Cronquist, Arthur.  
1945. Studies in the Sapotaceae. III. Dipholis and Bumelia. *J. Arnold Arb.* XXVI:435-471.
6. Kukachka, B. F.  
1977. Sectioning refractory woods for anatomical studies. USDA For. Serv. Res. Note FPL-0236. For. Prod. Lab., Madison, Wis. Also in *Micrographica Acta* 80:4:301-307, 1978.
7. Record, Samuel J.  
1939. American woods of the family Sapotaceae. *Tropical Woods* 59:21-51.