

AD-A069 705

NAVAL RESEARCH LAB WASHINGTON DC  
SURVEY OF POSTIRRADIATION HEAT TREATMENT AS A MEANS TO MITIGATE--ETC(U)  
FEB 79 J R HAWTHORNE  
NRC-RES-79-103

F/G 18/8

UNCLASSIFIED

NRL-8287

NUREG-CR-0486

NL

| OF |  
AD  
A069 705



END  
DATE  
FILMED  
7-79  
DDC

ADE 000 301

12 LEVEL III

NUREG/CR 0486  
NRL Report 8257

AD A 069705

# Survey of Postirradiation Heat Treatment as a Means to Mitigate Radiation Embrittlement of Reactor Vessel Steels


J. R. HAWTHORNE

*Thermostuctural Materials Branch  
Material Science and Technology Division*

February 14, 1979

Prepared for U.S. Nuclear Regulatory Commission

DDC FILE COPY

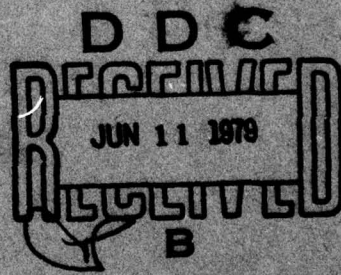

NAVAL RESEARCH LABORATORY  
Washington, D.C.

70 03 23 047

Approved for public release; distribution unlimited.

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, or any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for any third party's use, or the results of such use, of any information, apparatus, product or process disclosed in this report, or represents that its use by such third party would not infringe privately owned rights.

Available from:  
U.S. Nuclear Regulatory Commission  
Washington, DC 20555

Available from:  
National Technical Information Service  
Springfield, Virginia 22161

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER NUREG/CR 0486; NRL Report 8287	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) SURVEY OF POSTIRRADIATION HEAT TREATMENT AS A MEANS TO MITIGATE RADIATION EMBRITTLEMENT OF REACTOR VESSEL STEELS	5. TYPE OF REPORT & PERIOD COVERED Progress report on one phase of a continuing NRL Problem	
	6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) J. R. Hawthorne	8. CONTRACT OR GRANT NUMBER(s) NRC-RES-79-103, NRC-03-76-0348	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Naval Research Laboratory Washington, DC 20375	10. PROGRAM ELEMENT PROJECT, TASK AREA & WORK UNIT NUMBERS NRL Problem M01-40 (See item 18)	
11. CONTROLLING OFFICE NAME AND ADDRESS US Nuclear Regulatory Commission Reactor Safety Research Division and Operating Reactors Division Washington, DC 20555	12. REPORT DATE February 14, 1979	
	13. NUMBER OF PAGES 32	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) UNCLASSIFIED	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Prepared for the U.S. Nuclear Regulatory Commission, Reactor Safety Research Division under Interagency Agreement RES-79-103 and for the Operating Reactors Division under Interagency Agreement NRC-03-76-0348.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Charpy-V properties    A302-B steel    Postirradiation heat treatment Embrittlement relief    A533-B steel    Radiation embrittlement Fracture resistance    A508-2 steel    Pressure vessel steels Notch ductility    Weld metals Nuclear reactors		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) → Postirradiation heat treatment (annealing) is being investigated as a method for the alleviation of radiation embrittlement to reactor vessel steels. Objectives of this study were to identify those service and metallurgical variables which can affect annealing response, to report data comparisons available for qualification of suspected influences, and to survey experimental results from commercially produced reactor materials and duplicate materials from the laboratory. → (Continues)		

D D C  
RECEIVED  
JUN 11 1979  
B

79 03 23 0487

20. Abstract (Continued)

Twelve factors are identified as having potential for affecting the postirradiation heat treatment response of low-alloy pressure vessel steels. A tentative qualification of six factors as significant contributing variables is made on the basis of experimental comparisons. Of these, heat-treatment temperature was observed to exert the largest influence on the embrittlement relief by annealing. The evidence indicates that a 399°C heat treatment, but not a 343°C heat treatment, is a practical and effective method for reducing and controlling radiation embrittlement in reactor vessels.

## CONTENTS

INTRODUCTION .....	1
POTENTIAL FACTORS INFLUENCING HEAT-TREATMENT RESPONSE .....	2
PRESENT QUALIFICATION OF SUSPECT VARIABLES .....	3
Irradiation Temperature .....	3
Neutron Fluence .....	8
Relative Radiation Resistance .....	8
Applied Stress .....	8
Residual Element Composition .....	10
Alloy Element Composition .....	14
Product Form .....	14
Heat-Treatment Temperature .....	15
Heat-Treatment Duration .....	15
Cyclic Irradiation and Annealing .....	16
SURVEY OF EXPERIMENTAL ANNEALING RESULTS .....	20
SUMMARY .....	26
ACKNOWLEDGMENTS .....	28
REFERENCES .....	28

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/ _____	
Availability Codes	
Dist	Avail and/or special
A	

90

**SURVEY OF POSTIRRADIATION HEAT TREATMENT  
AS A MEANS TO MITIGATE RADIATION EMBRITTLEMENT  
OF REACTOR VESSEL STEELS**

**INTRODUCTION**

Nuclear-radiation service typically produces a progressive reduction in the notch ductility of low-alloy steels. The reduction is manifested by a decrease in Charpy-V ( $C_v$ ) upper-shelf energy level and by an elevation in temperature of the ductile-to-brittle transition. Postirradiation heat treatment (annealing) is being investigated as a method for the reversal of these detrimental radiation effects for reactor-vessel steels. This study was undertaken to analyze factors which could affect annealing response, report data available to qualify suspected influences on annealing, and summarize experimental results generated for many commercially produced reactor materials and companion materials produced in the laboratory.

The degradation of notch ductility by radiation is recognized by the ASME Code (Section III) [1] and by the Code of Federal Regulations (10CFR50) [2], and direct and indirect limitations are imposed on postirradiation properties. For example a  $C_v$  upper-shelf energy of at least 68 J (50 ft-lb) is required by the ASME Code by its use of this energy level to index the reference nil-ductility temperature,  $RT_{NDT}$ , for fracture toughness characterization. If notch ductility properties fall below Code requirements, application of an in-service heat treatment is one option open for extending vessel life. That is, the Code of Federal Regulations states: "Reactor vessels for which the predicted value of adjusted reference temperature exceeds 96°C (200°F) shall be designed to permit a thermal annealing treatment to recover material toughness properties." An alternate option involves performing an essentially complete volumetric inspection of the beltline region of the vessel and development of a fracture mechanics analysis which "conservatively demonstrates, making appropriate allowances for all uncertainties, the existence of adequate margins for continued operations" [2].

At present, there is little doubt that Code notch ductility requirements can be met by recently constructed reactor vessels over projected service lifetimes. A concern does exist, however, for certain vessels produced prior to 1971 which did not have the benefit of current radiation effects technology. Here, a combination of factors including high copper and phosphorus contents and low initial  $C_v$  upper-shelf energy level may exist which could bar meeting the Code criteria after some period of vessel operation. A high content of copper and phosphorus impurities in steel is known to contribute a high sensitivity to radiation-induced reductions in notch ductility. A low upper-shelf energy, in addition, provides less of a margin for radiation-induced degradation. NRC Regulatory Guide 1.99 [3] is available for predicting radiation effects to reactor vessel steels from knowledge of the steel composition and the expected neutron-fluence accumulation by the vessel.

Manuscript submitted October 10, 1978.

## HAWTHORNE

Existing data on recovery of notch ductility with postirradiation heat treatment are quite limited and are largely in the form of  $C_v$  data. For the most part those data developed prior to 1972 represent only spot tests of annealing response and thus do not fully describe upper-shelf and transition behavior. Increased interest in the annealing method since 1972 has led to specific studies of annealing behavior. More importantly, current studies are including compact specimens (CS) for fracture toughness ( $K_{Ic}$ ,  $K_{Jd}$ ,  $K_{Jd}$ ) determinations [4-7]. Initial CS results from U.S. programs are expected in 1979 and 1980. To guide the investigations, important data trends have been discerned from the existing  $C_v$  data, as reported below.

A discussion of vessel annealing operations is beyond the scope of this report; however, two annealing options appear to be available to reactors. Heat treatments at temperatures up to 343°C (650°F) represent one option, with primary-pump or nuclear heating being used to attain the requisite temperature in the vessel. With this option the reactor coolant and the core internals would be left in place. This annealing option has already been successfully used for a pressurized water reactor (Army SM-1A reactor) [8, 9]. In this case, however, the vessel operating temperature of 221°C (430°F) was significantly lower than that of commercial power reactors, 288°C (550°F).

The second option involves the use of auxiliary heaters to bring the vessel (or selected components thereof) to a higher annealing temperature, such as 399°C (750°F). Higher temperatures can result in greater recovery of properties, but removal of the core internals as well as the coolant would be required. For most reactors the mechanics of annealing at temperatures significantly above 399°C (750°F) or 427°C (800°F) would appear to be prohibitive.

### POTENTIAL FACTORS INFLUENCING HEAT-TREATMENT RESPONSE

Several variables are considered to have potential for influencing notch ductility recovery by postirradiation heat treatment. By category these include

#### Service Variables

- Irradiation temperature,
- Neutron fluence,
- Relative radiation resistance,
- Applied stress,

**Steel Metallurgy**

Impurity element composition (including Cu, P, S),

Alloy element composition,

Product form (plate, weld, or forging),

**Heat Treatment**

Annealing temperature,

Annealing time,

**Cyclic Irradiation and Annealing Conditions**

Annealing time and temperature,

Fluence before first anneal, and

Fluence between anneals.

Synergistic effects between variables are also considered possible.

**PRESENT QUALIFICATION OF SUSPECT VARIABLES**

Experimental data are available from 288°C radiation experiments (accelerated-test reactor irradiations) to directly or indirectly test the contribution of some suspect variables. It is emphasized that the observations are tentative in some cases and require confirmatory tests.

**Irradiation Temperature**

Notch ductility recovery with 343 to 427°C postirradiation heat treatments appears to increase with decreasing irradiation temperature in the range of 343 to 121°C. Experimental results in support of this indication are given in Figs. 1 through 6. The figures index the irradiation and annealing effect to the conventional (arbitrary)  $C_v$  41-J (30 ft-lb) transition temperature; however, transition-temperature changes measured at  $C_v$  41J and  $C_v$  68-J energy indices show good agreement in most cases. Figures 1 to 5 show results for the ASTM A302-B reference plate [10]. Figure 6 shows results for two A533-B Class 1 plates from the same (split) steel melt [12]. (The data of Figs. 1 and 2 and of Figs. 3 and 4 were developed using one irradiation assembly with two-zone temperature control. Likewise, the data of Fig. 6 were developed with a single irradiation experiment.)

HAWTHORNE

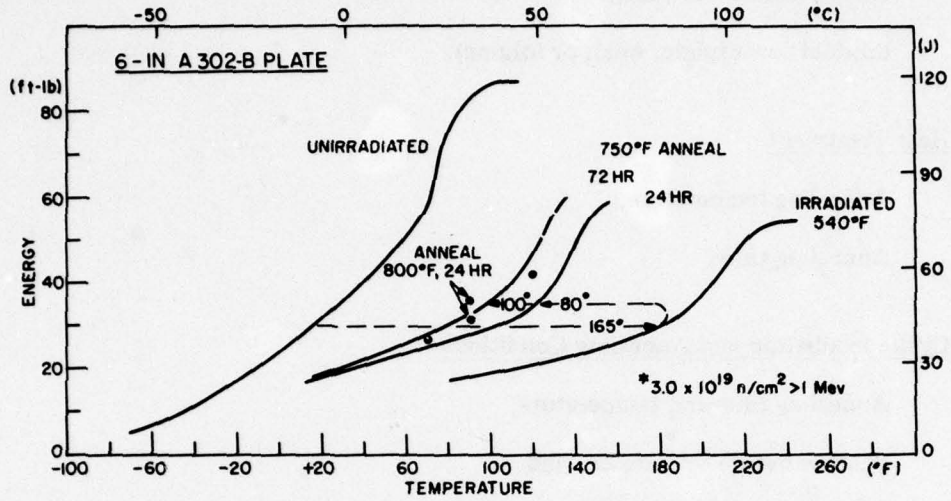


Fig. 1 — Response of the ASTM A302-B reference plate to various low-temperature heat treatments after 282°C (540°F) irradiation (experiment A). (From Ref. 10.)

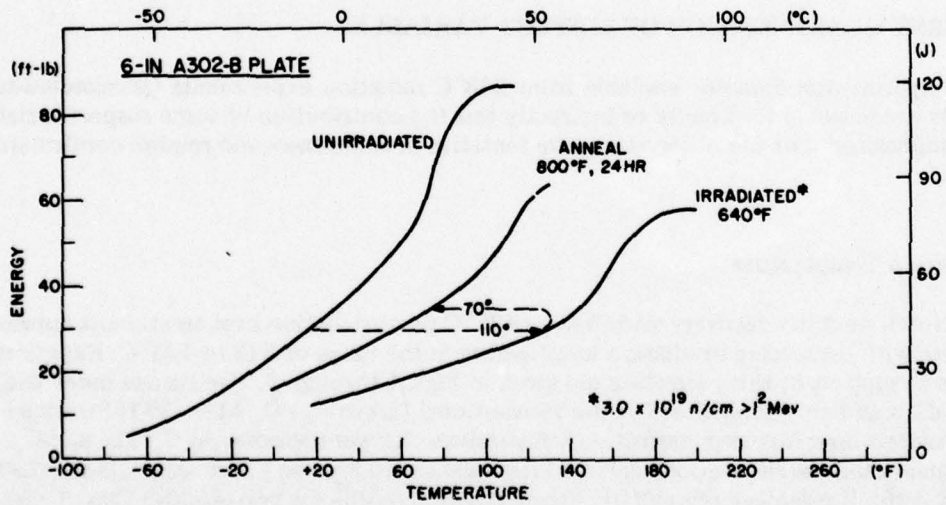


Fig. 2 — Response of the ASTM A302-B reference plate to a 427°C (800°F) heat treatment after 338°C (640°F) irradiation (experiment A; see Fig. 1 also)

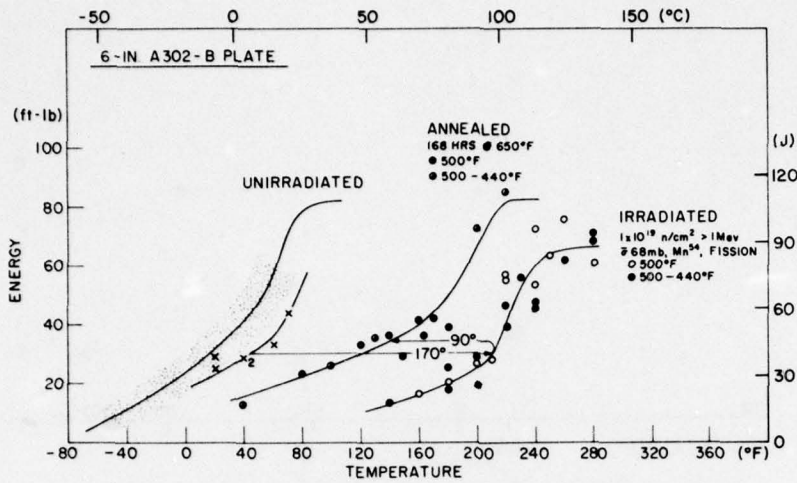


Fig. 3 — Charpy-V-notch ductility behavior of the ASTM A302-B reference plate before and after irradiation at a constant temperature of 260°C (500°F) and under cyclic temperature conditions ranging from 260 to 227°C (500 to 440°F). Responses of both steel conditions to 343°C (650°F) postirradiation annealing for 168 hr are also shown. The x data points depict the unirradiated behavior of the particular section of A302-B steel used for this experiment (experiment B). (From Ref. 11.)

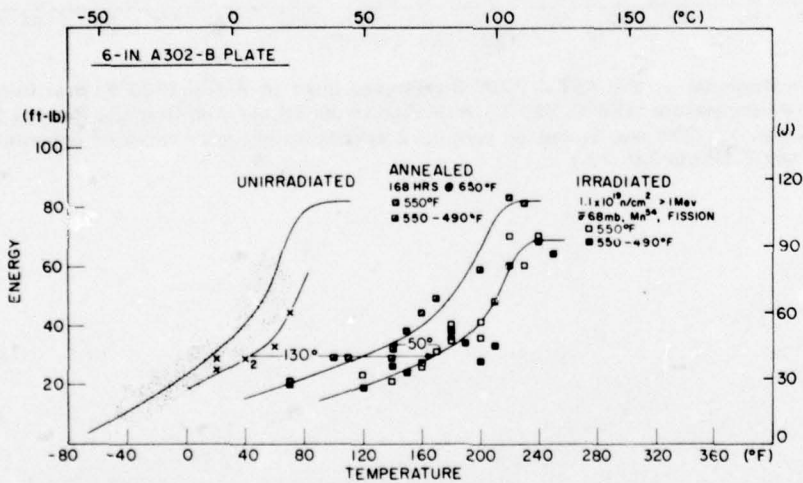


Fig. 4 — Charpy-V-notch ductility behavior of the ASTM A302-B reference plate before and after irradiation at a constant 288°C (550°F) and under cyclic temperature conditions ranging from 288 to 254°C (550 to 490°F). Responses of both steel conditions to 343°C (650°F) postirradiation annealing for 168 hr are also shown. The x data points depict the unirradiated behavior of A302-B steel used for this experiment (experiment B; see Fig. 3 also). (From Ref. 11.)

HAWTHORNE

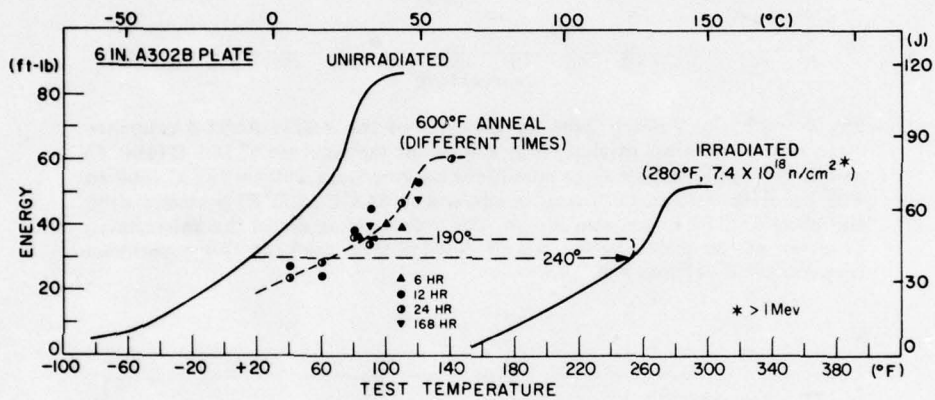


Fig. 5 — Response of the ASTM A302-B reference plate to 316°C (600°F) heat treatment after low-temperature (138°C, 280°F) irradiation in the Brookhaven Graphite Reactor (BGR) (experiment C). The results can be compared approximately with those of experiment B, Figs. 3 and 4. (From Ref. 10.)

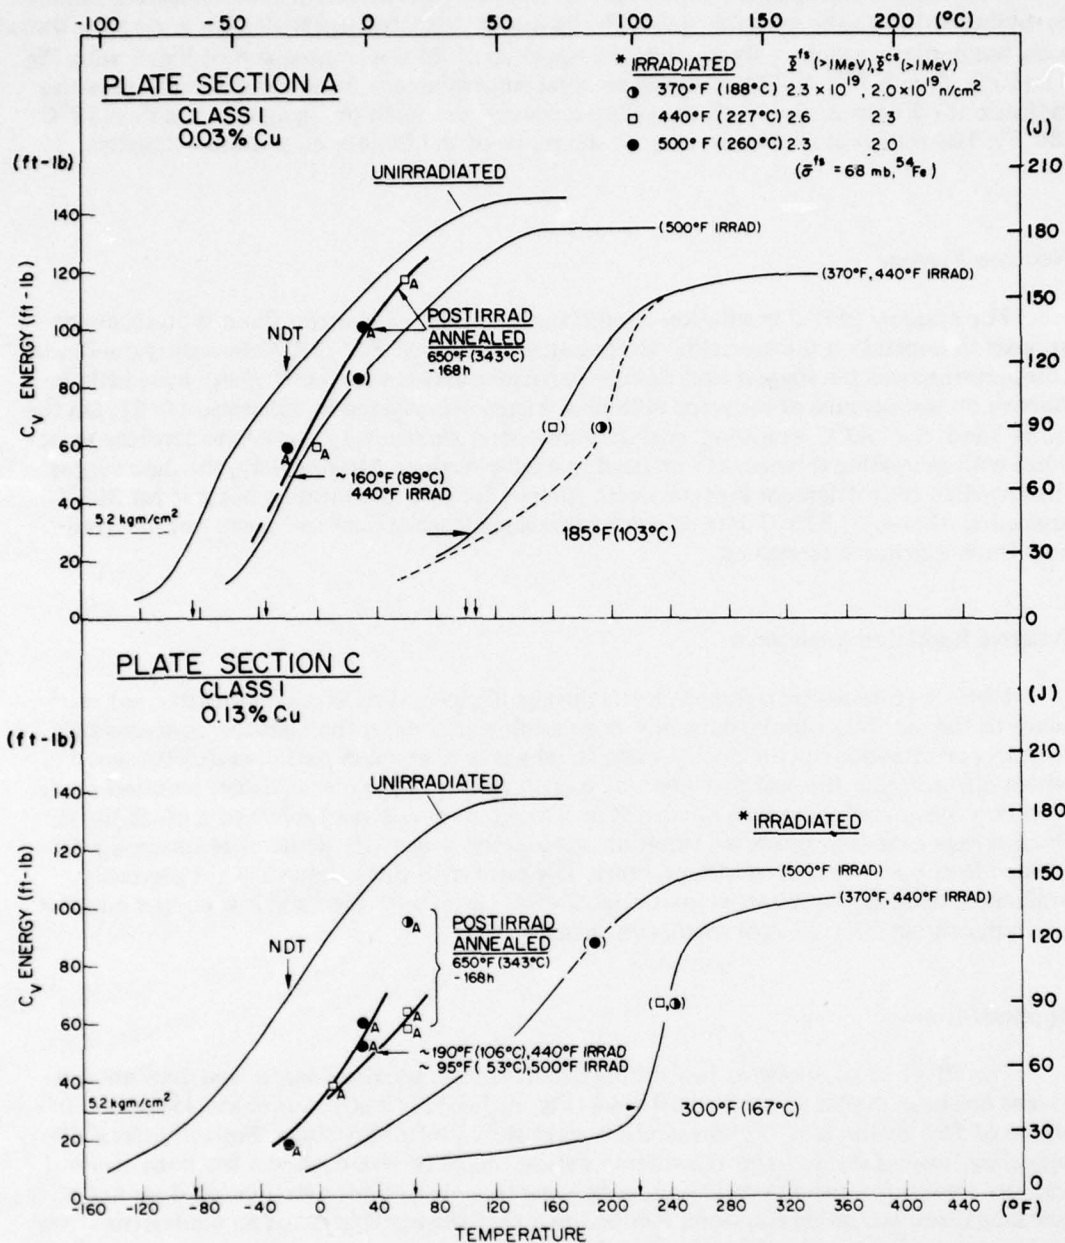


Fig. 6 - Charpy-V-notch ductility recovery in two plates from a split melt of A533-B steel (different copper contents) with 343°C (650°F) 168-hr heat treatment following irradiation at different temperatures. Greater residual embrittlement after heat treatment is observed for the plate with the higher copper content (plate section C). (From Ref. 12.)

## HAWTHORNE

The effect of irradiation temperature on residual embrittlement after annealing cannot be established from the available data. The data are too limited and typically concern the transition-temperature regime only and not the upper shelf. In the comparison of Fig. 1 with Fig. 2 and Fig. 3 with Fig. 4, differences in residual embrittlement from transition temperature indications ( $\Delta T$  irradiation— $\Delta T$  annealing recovery) are small or negligible: less than 17°C (30°F). The similarity, however, may be the result of the fluence conditions evaluated.

### Neutron Fluence

For nominal 288°C irradiation conditions the effect of neutron fluence on recovery appears to depend on the annealing temperature employed. For 343°C annealing the limited comparisons available suggest that fluence variations above  $\approx 1 \times 10^{19}$  n/cm<sup>2</sup> have little influence on the amount of recovery obtained. Figure 7 is offered in illustration [13]. On the other hand, for 399°C annealing, transition-temperature recovery appears to increase somewhat with increasing fluence, as discussed in a later section. Alternatively, the data suggest that residual embrittlement increases with fluence for 343°C annealing but not for 399°C annealing. However, 399°C data sets reflecting large fluence differences are not yet available for a conclusive assessment.

### Relative Radiation Resistance

Distinct from neutron fluence level, the significance of radiation embrittlement resistance to the recovery obtained has not been established. Here, the question concerns the relative performance of two steels, A and B, which have equal radiation embrittlement but which differ in that the embrittlement of steel A (high radiation sensitivity) required a low-fluence exposure whereas that of steel B (intermediate sensitivity) required a much higher fluence exposure. The proposed variation in radiation sensitivity could arise through a difference in copper content or other factors. The answer to this question is not presently available; however, experiments involving A302-B plates with high and low copper content are underway at NRL to explore this uncertainty [14].

### Applied Stress

The effect of an applied stress during irradiation on postirradiation heat-treatment response has been explored for A302-B steel (Fig. 8) [15]. The stress level employed was in excess of 75% of the 288°C preirradiation yield strength (0.2% offset). Following 399°C annealing, essentially full transition-temperature recovery was observed for both stressed and unstressed (reference) conditions, suggesting that stress during irradiation does not alter postirradiation annealing response. It is believed that the application of an equivalent stress during the anneal would not have affected the outcome.

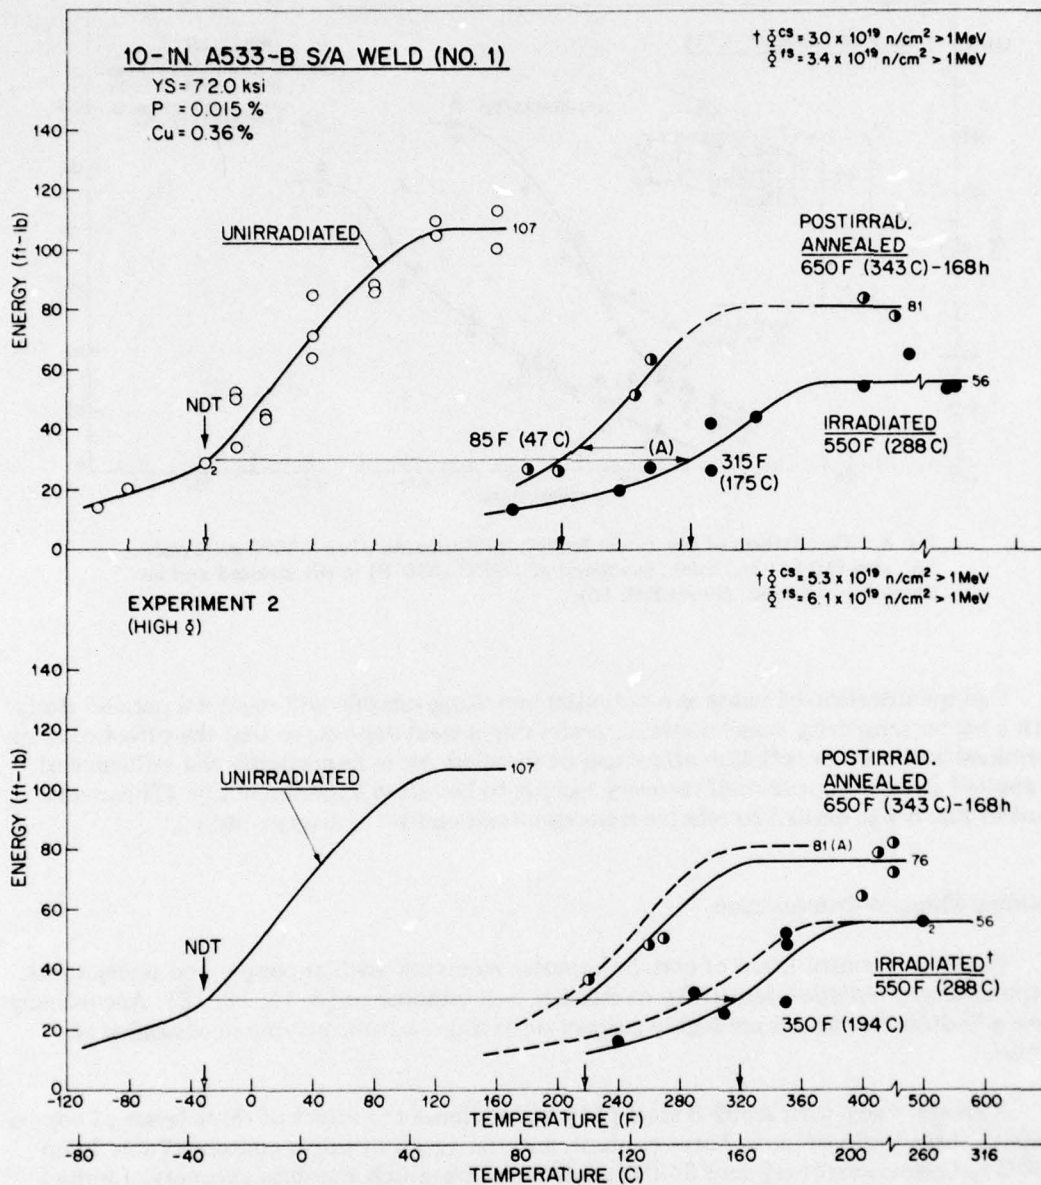


Fig. 7 - Notch ductility of weld 1 (series 1) before and after irradiation to two fluence levels. Notch ductility recovery with 343°C (650°F) 168-hr heat treatment is also shown. (From Ref. 13.)

## HAWTHORNE

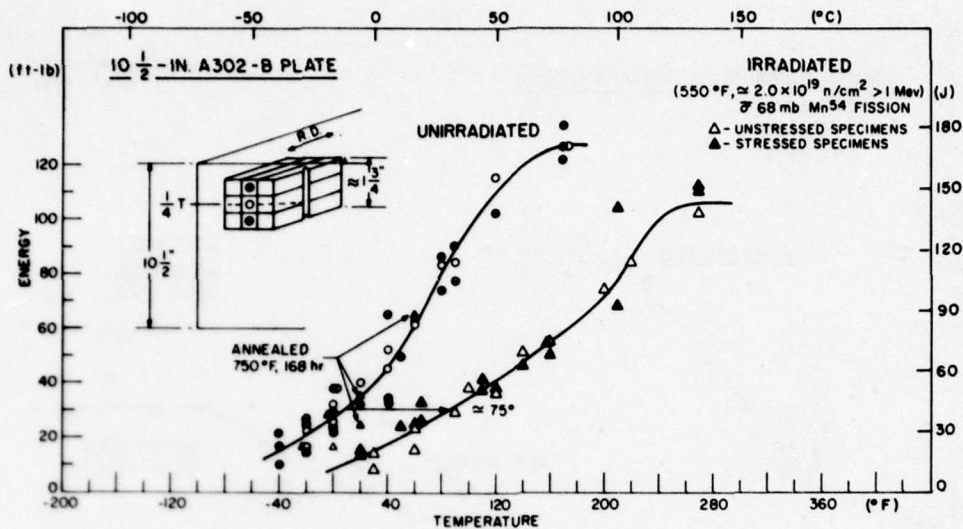


Fig. 8 — Comparison of the notch ductility performance of an A302B steel plate, 267 mm (10-1/2 in.) thick, irradiated at 288°C (550°F) in the stressed and unstressed conditions. (From Ref. 15).

Full qualification of stress as a potential annealing variable will require a parallel study with a higher sensitivity vessel material, preferably a weld deposit, so that the effect of stress combined with a large radiation effect can be revealed. More importantly the influence of an applied stress on upper-shelf recovery has yet to be tested experimentally. (The assessment in Fig. 8 was limited to relative transition-temperature recovery only.)

### Residual Element Composition

The strong contribution of certain impurity elements, such as copper and phosphorus, to the observed radiation sensitivity of steels is well established [3, 12, 13, 16]. Accordingly these and other impurities are highly suspect of having a significant role in annealing response.

A recent study with A302-B steel [14] has explored the effect of three levels of copper content, three levels of phosphorus content, and two levels of sulfur content (Table 1) on 288°C radiation sensitivity and 343°C postirradiation notch ductility recovery. Limited tests of the 343°C annealed condition were also conducted. Figures 9, 10, and 11 show the findings on transition-temperature change for the test plates. Full upper-shelf recovery with 343°C annealing was reported for all but one of the plates (composition V67).

Table 1 — Chemical Composition of A302-B Plates

Plate Code	Melt No.	Cast No.	Chemical Composition (wt-%) <sup>a</sup>								
			S	P	Cu	C	Mn	Si	Mo	Al <sup>b</sup>	N
V61	1	1	0.017	0.002	0.15	0.23	1.38	0.26	0.50	0.028	0.001
V63	1	2	0.017	0.014	0.15	0.24	1.28	0.26	0.49	0.029	0.002
V65	1	3	0.017	0.024	0.16	0.24	1.36	0.26	0.50	0.029	0.001
V67	1	4	0.017	0.024	0.29	0.24	1.37	0.26	0.50	0.028	0.001
V71	2	1	0.029	0.016	0.045	0.25	1.23	0.25	0.49	0.027	0.001
V73	2	2	0.029	0.016	0.16	0.25	1.23	0.25	0.49	0.027	0.001
V75	2	3	0.029	0.016	0.30	0.25	1.23	0.25	0.49	0.027	0.001
V77	2	4	0.029	0.024	0.30	0.25	1.23	0.25	0.49	0.027	0.001
A302-B Specification			<u>0.040</u> max.	<u>0.035</u> max.	—	<u>0.25</u> max.	<u>1.15</u> 1.50	<u>0.15</u> 0.30	<u>0.45</u> 0.60	—	—

<sup>a</sup>Ladle analyses by U.S. Steel Corporation.

<sup>b</sup>Total aluminum.

Several experimental determinations were accomplished by the study. First, the effectiveness of 343°C annealing was shown to be relatively independent of copper, phosphorus, or sulfur content for the composition range investigated. Second, the absolute transition-temperature recoveries of the test plates were found to be relatively independent of the magnitude of the prior transition-temperature elevation by irradiation. This observation indirectly suggests that absolute recovery with 343°C annealing is also relatively independent of fluence level. (In Figs. 9 and 10 overall differences in transition temperature elevation approach a factor of 2.) With higher temperature annealing (Fig. 11) a comparable independence of recovery on prior radiation embrittlement was noted. One exception was found in plate V63, for which an explanation could not be offered. A third observation was that a high (0.30%) copper content is detrimental to upper-shelf recovery (343°C annealing) when the steel has a sulfur content on the order of 0.017% S. In contrast, phosphorus was found to have neither a positive or negative effect on recovery for the compositions investigated.

This recent study clearly provides valuable new information on impurity element contributions and annealing trends. The findings however require confirmation for other types of vessel steels and weld metals. In particular, the role of copper and phosphorus in upper-shelf recovery of weld metals requires more detailed study.

HAWTHORNE

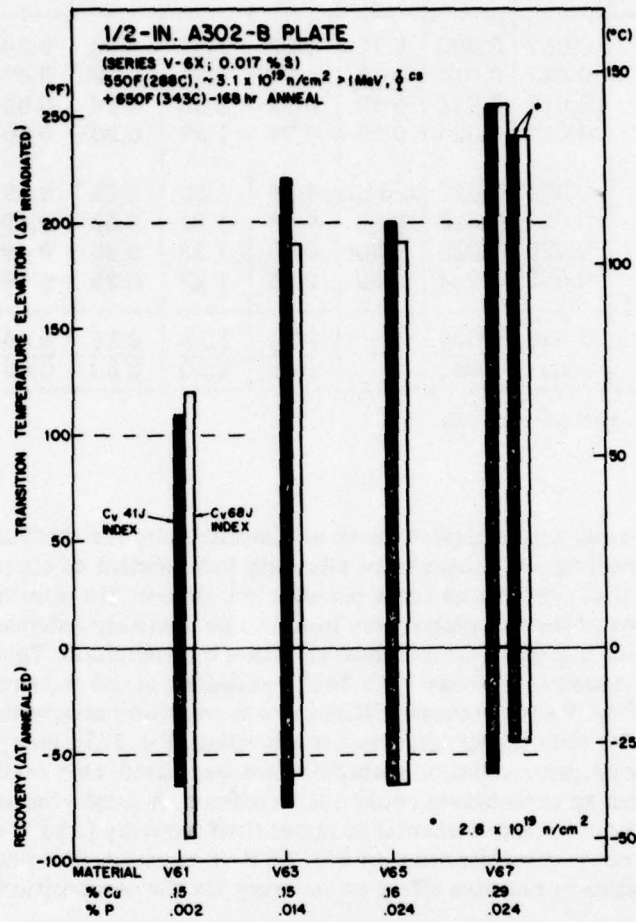


Fig. 9 - Summary of Charpy-V transition-temperature changes (41-J and 68-J indices) of plate series V6X with 288°C (550°F) irradiation and with 343°C (650°F) postirradiation heat treatment. (From Ref. 14.)

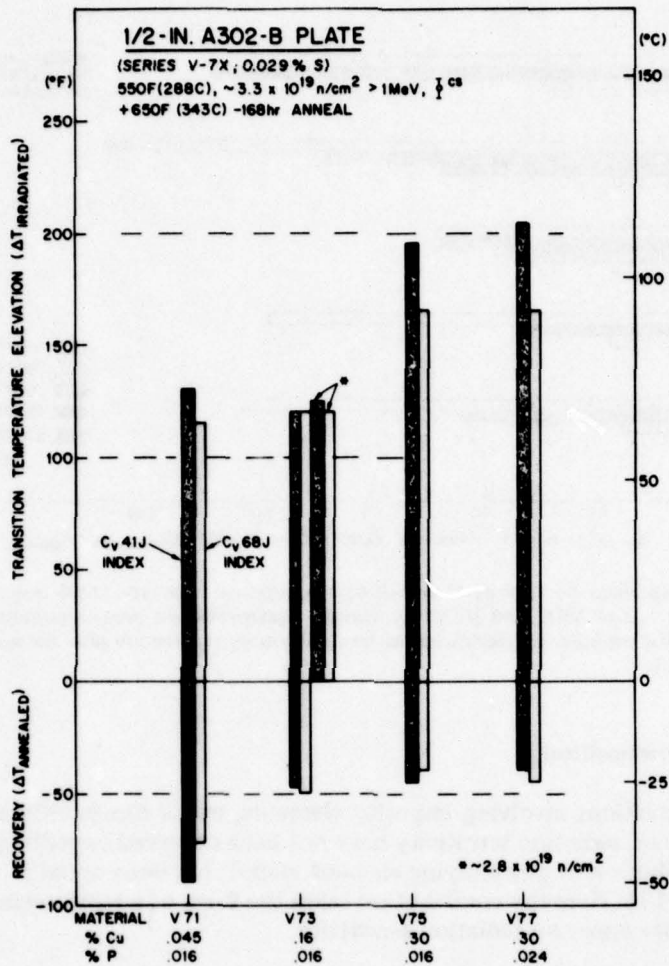


Fig. 10 - Summary of Charpy-V-notch transition-temperature changes (41-J and 68-J indices) of plate series V7X with 288°C (550 F) irradiation and with 343°C (650 F) postirradiation heat treatment. (From Ref. 14.)

## HAWTHORNE

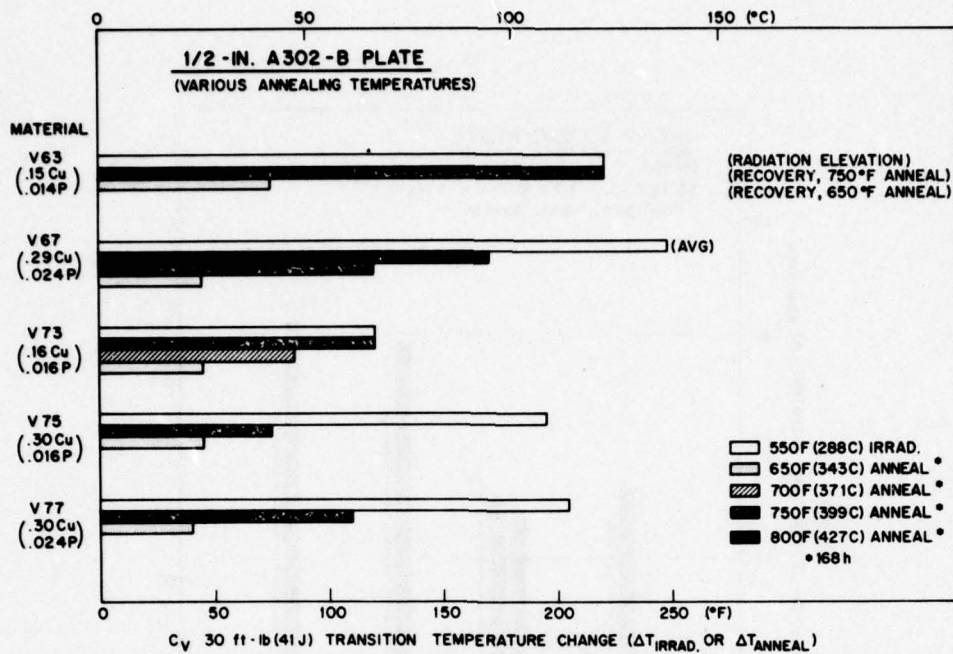


Fig. 11 — Comparison of Charpy-V transition-temperature recovery (41-J index) produced in selected plates (series V6X and V7X) by various postirradiation heat-treatment temperatures. The initial radiation-induced elevations in transition temperature are also shown for reference. (From Ref. 14.)

### Alloy Element Composition

Unlike observations involving impurity elements, major direct influences of specific alloying elements on radiation sensitivity have not been observed experimentally. However, an indirect contribution of one alloying element, nickel, has been noted in weld deposit assessments [13, 17]. Here the contribution takes the form of a reinforcement of the detrimental effect of copper on radiation sensitivity.

Data to test the general effects of alloying-element variations in A302-B, A533-B, and A508-2 steels and companion weld metals (submerged arc, manual metal arc deposits) are not currently available. Clarification of the role of certain elements including manganese, chromium, and molybdenum as well as nickel would appear to be in order in view of unexplainable differences noted among typical materials.

### Product Form

The significance of product form (plate, weld, or forging) to postirradiation heat-treatment response has not been tested directly. Further, a judgment on this variable cannot be made from the data compiled in this report.

**Heat-Treatment Temperature**

It has been observed that the heat-treatment temperature must exceed the prior irradiation temperature to obtain measurable transition-temperature recovery or recovery of upper-shelf energy. For 288°C irradiation conditions it has also been demonstrated that notch ductility recovery increases with increasing temperature above 288°C but not linearly (Figs. 1 and 11). Significantly, full upper-shelf recovery can be obtained at a lower temperature than full transition-temperature recovery. For example, 343°C annealing produced full upper-shelf recovery for all but one of the plates of the A302-B melt series (Table 1) but only small transition-temperature recovery [14]. Accordingly the kinetics of upper-shelf recovery appear to be different from that of transition-temperature recovery. Finally, as demonstrated in Figs. 1 and 11, a heat treatment of 427°C following 288°C irradiation may not be sufficiently high in temperature to produce full transition-temperature recovery.

**Heat-Treatment Duration**

Sufficient data exist to show that a heat-treatment period of 168 hr (1 week) is about optimum for the annealing of plate and weld-deposit materials following 288°C irradiation. Experimental results in support of this assessment are shown in Figs. 1, 12, and 13. For heat-treatment periods shorter than 168 hr, an increase in annealing time generally results in increased recovery (Fig. 1). Extension of the heat-treatment period beyond 168 hr, on the other hand, does not produce a significant increase in either transition-temperature recovery or upper-shelf energy (Figs. 12 and 13) [4]. The data of Fig. 5 would appear to be in conflict with the preceding conclusion on optimum annealing time; however, the irradiation temperature employed was only 138°C (280°F).

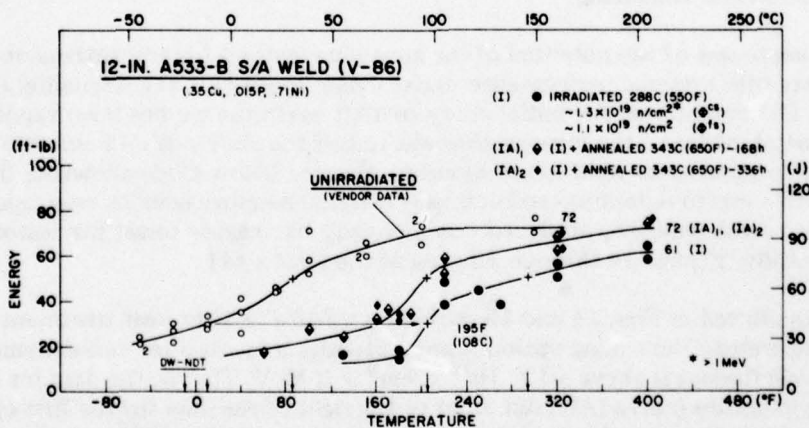


Fig. 12 - Notch ductility recovery of weld V86 by 343°C (650°F) annealing heat treatment for two different times following first-cycle irradiation. (From Ref. 4.)

## HAWTHORNE

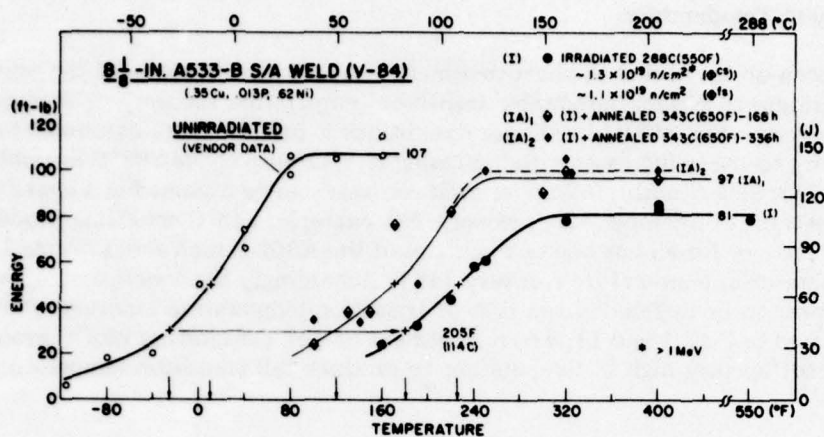


Fig. 13 - Notch ductility recovery of weld V84 by 343°C (650°F) annealing heat treatment for two different times following first-cycle irradiation. (From Ref. 4.)

A 168-hr heat treatment undoubtedly will represent only a small fraction of the total time involved in preparing a reactor system for annealing and in bringing the reactor vessel to temperature. Accordingly a heat-treatment duration of 168 hr is not considered to be overly long from an operations standpoint. Equally important the possibility for falling short of a recovery target becomes significantly less with a 168-hr anneal than with a much shorter heat treatment.

### Cyclic Irradiation and Annealing

The ultimate test of the potential of the annealing method for embrittlement relief obviously rests with material performance under cyclic irradiation (I), annealing (A), and reirradiation (R) conditions. An initial study of IAR performance has been reported by NRL [4]. One objective of the investigation was to test the ability of 343 and 399°C intermediate heat treatments to hold notch ductility changes below Code-allowable limits. A second objective was to determine and compare material reembrittlement rates upon reirradiation. Two weld deposits, produced commercially by reactor vessel fabricators, were used for the study. Figures 14 through 18 present the results [4].

The data plotted in Figs. 14 and 15 show that a 343°C 168-hr heat treatment depicting the "low temperature" annealing option is not a promising method for embrittlement relief if the first-cycle fluence is above  $\approx 1 \times 10^{19} \text{ n/cm}^2 > 1 \text{ MeV}$ . That is, the data for the second-cycle exposure (curve IAR) fall on or to the right of the data for the first-cycle exposure (curve I). In this case the second-cycle fluence was only  $3 \times 10^{18} \text{ n/cm}^2 > 1 \text{ MeV}$ . In contrast (Figs. 16 and 17) a 399°C 168-hr heat treatment representing the "high temperature" option proved to be quite effective in reducing the buildup of radiation effects. Transition-temperature changes observed with IAR are summarized in Fig. 18. The data trends clearly show that the rate of reembrittlement after annealing is greater than the rate

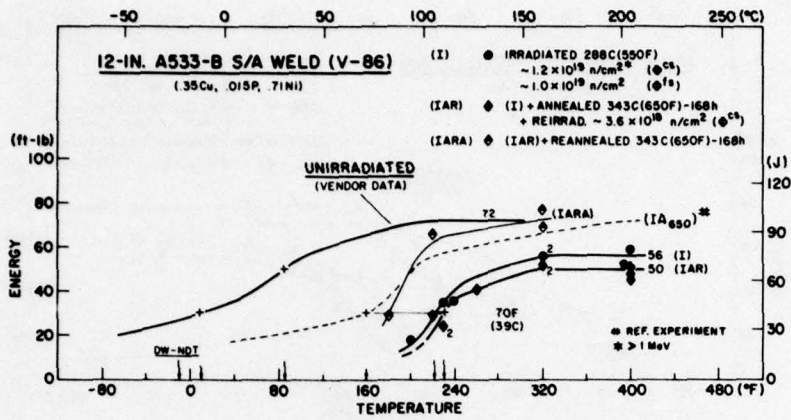


Fig. 14 - Notch ductility behavior of weld V86 after reirradiation following a midcycle 343°C (650°F) annealing heat treatment (curve IAR) and after reirradiation and reheat treatment at 343°C (650°F) (curve IARA). The notch ductility of the weld after the first-cycle irradiation (curve I) and after the first-cycle heat treatment (curve IA, reference experiment) are also shown. (From Ref. 4.)

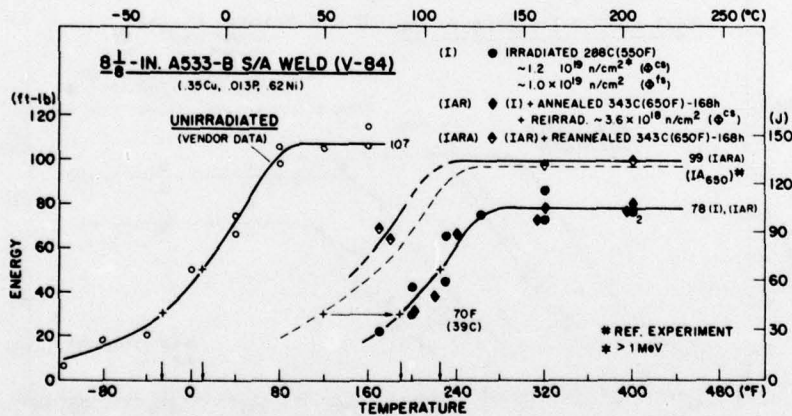


Fig. 15 - Notch ductility behavior of weld V84 after reirradiation following midcycle 343°C (650°F) annealing heat treatment (curve IAR) and after reirradiation and reheat treatment at 343°C (650°F) (curve IARA). The notch ductility of the weld after the first-cycle irradiation (curve I) and after the first-cycle heat treatment (curve IA, reference experiment) are also shown. (From Ref. 4.)

HAWTHORNE

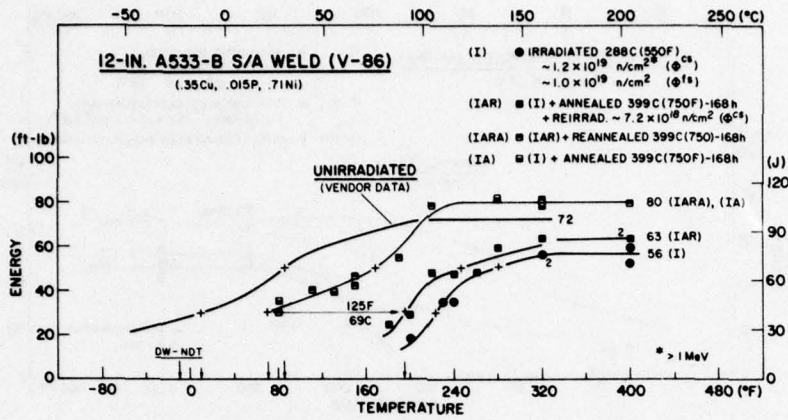


Fig. 16 — Notch ductility behavior of weld V86 after reirradiation following a midcycle 399°C (750°F) annealing heat treatment (curve IAR) and after reirradiation and reheat treatment at 399°C (750°F) (curve IARA). The notch ductility of the weld after the first-cycle irradiation (curve I) and after the first-cycle heat treatment (data points IA) are also shown. (From Ref. 4.)

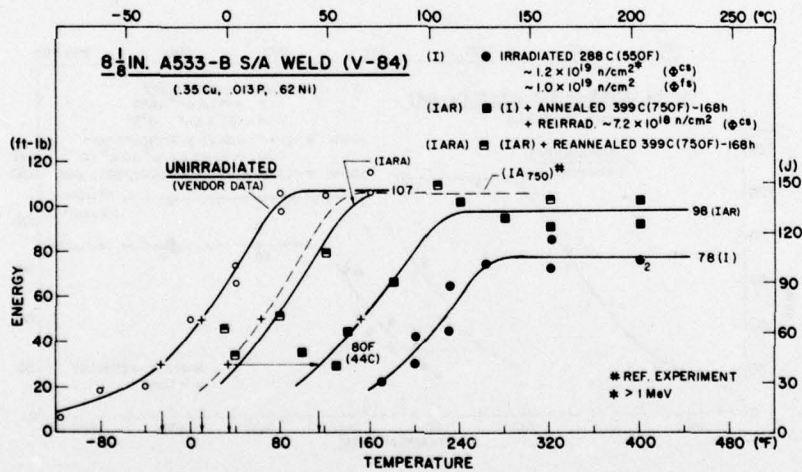


Fig. 17 — Notch ductility behavior of weld V84 after reirradiation following a midcycle 399°C (750°F) annealing heat treatment (curve IAR) and after reirradiation and reheat treatment at 399°C (750°F) (curve IARA). The notch ductility of the weld after the first-cycle irradiation (curve I) and after the first-cycle heat treatment (curve IA) are also shown for reference. (From Ref. 4.)

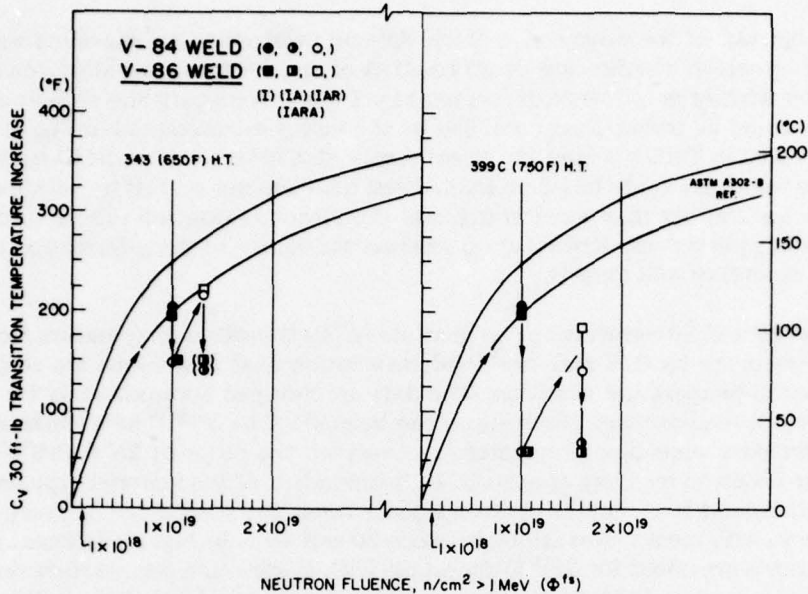


Fig. 18 - Transition-temperature behavior of welds V84 and V86 with 288°C (550°F) irradiation and 343°C (650°F) annealing and with 288°C (550°F) irradiation and 399°C (750°F) annealing (two cycles each). The shaded band refers to the transition-temperature trend of the ASTM A302-B reference plate with < 232°C (450°F) irradiation. (From Ref. 4.)

of embrittlement experienced by nonannealed material. Moreover the trends suggest that that "damage" most readily introduced into the material (that produced early in radiation service) is also that "damage" most readily removed by annealing. This projection is based in part on the similarity of the radiation embrittlement rates observed for the annealed material and the virgin material.

Important insight into IAR performance has been secured with the preceding results; however, additional tests of IAR trends are necessary. At the same time, it must be recognized that reactor experiment operations required by IAR studies are time consuming and much more complex than I or IA experiment operations. Thus, a large volume of data of this type cannot be expected soon. One question which needs an early answer is whether 343°C annealing has potential for reactor vessels having first-cycle fluences less than  $1 \times 10^{19}$  n/cm<sup>2</sup>. Also, Figs. 14 and 15 show that upper-shelf changes with annealing cannot be predicted closely from transition-temperature changes. Accordingly upper-shelf IAR patterns must be established separately.

## SURVEY OF EXPERIMENTAL ANNEALING RESULTS

The objective of the survey of available data on postirradiation annealing was to reveal trends by which clarification or affirmation of the foregoing observations could be made and by which the influence of certain, as yet unresolved, variables such as composition effects could be tested. Data compiled by the survey are presented in Figs. 19 through 22 and are listed in Tables 2a and 2b. These survey data must be interpreted with caution, because the values are often based on limited test data and not on full-transition curves. Also, some uncertainty may exist in material chemical composition (Table 3) or initial (preirradiation) properties, depending on whether the source of the information is testing-laboratory reports or mill reports.

In Figs 19 and 20 observations on absolute ( $\Delta^{\circ}\text{C}$ ) transition-temperature recovery and percentage recovery by 343 and 399 $^{\circ}\text{C}$  postirradiation heat treatments are compared to prior transition-temperature elevation. The data are grouped approximately by neutron fluence level. Several primary observations can be made: The 343 $^{\circ}\text{C}$  heat treatment consistently produced a transition-temperature recovery on the order of 28 $^{\circ}\text{C}$  (50 $^{\circ}\text{F}$ )  $\pm$  16 $^{\circ}\text{C}$  (30 $^{\circ}\text{F}$ ). The observed recovery appears to be independent of the material type evaluated, its prior embrittlement level, and its neutron fluence level. The percentage recovery also shows a consistency, with most values falling between 20 and 40%. In Fig. 20 different relationships and trends are noted for 399 $^{\circ}\text{C}$  annealing. Higher transition-temperature recoveries are illustrated, as expected. Percentage recovery typically is about 55 to 75%. In this case a trend toward higher recovery with increasing fluence is suggested by the data. A greater spread in values ( $\pm 22^{\circ}\text{C}$  ( $\pm 40^{\circ}\text{F}$ )) is also shown, which could be indicating a composition effect or an effect of prior transition-temperature elevation. On the other hand, specific contributions of these variables are not evident from the data patterns.

Figures 21 and 22 compare upper-shelf recovery by annealing against the prior upper-shelf reduction by irradiation. For 343 $^{\circ}\text{C}$  annealing (Fig. 21) a wide variation in percentage recovery is observed, even though the percentage reductions by irradiation predominantly are in the range of 10 to 30%. Likewise the absolute recovery in upper-shelf energy does not show a particular dependence on the absolute reduction by irradiation. It is suspected that material variables are contributing to the observed differences in annealing response. Neutron fluence level, on the other hand, does not appear to be a critical variable. With 399 $^{\circ}\text{C}$  annealing (Fig. 22) essentially all of the materials showed full upper-shelf recovery. The exceptions to this trend, two high fluence points, may be due to the limited number of specimen tests performed. The influence of the prior upper-shelf reduction on subsequent recovery cannot be assessed in Fig. 22 because of the similarity of the radiation changes.

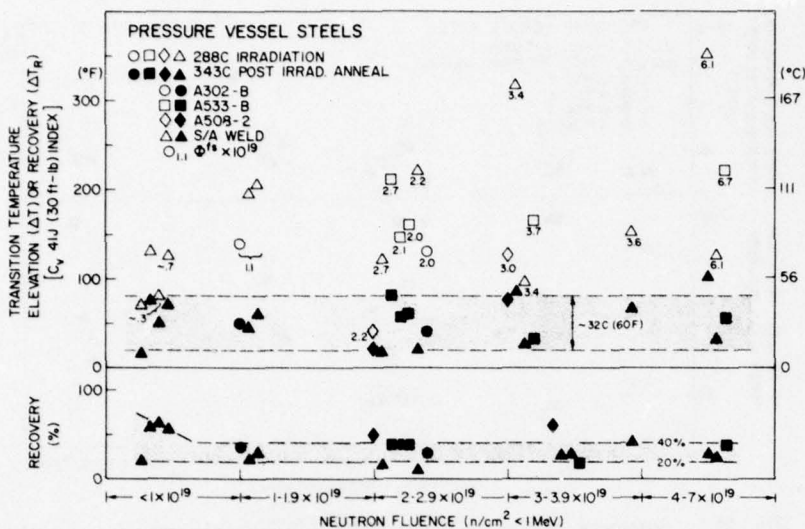


Fig. 19 — Summary of Charpy-V transition-temperature (41-J index) changes observed for several steels with 288°C (550°F) irradiation (open symbols) and with 343°C (650°F) postirradiation heat treatment (filled symbols). The shaded bands illustrate the general recovery trends with increasing fluence.

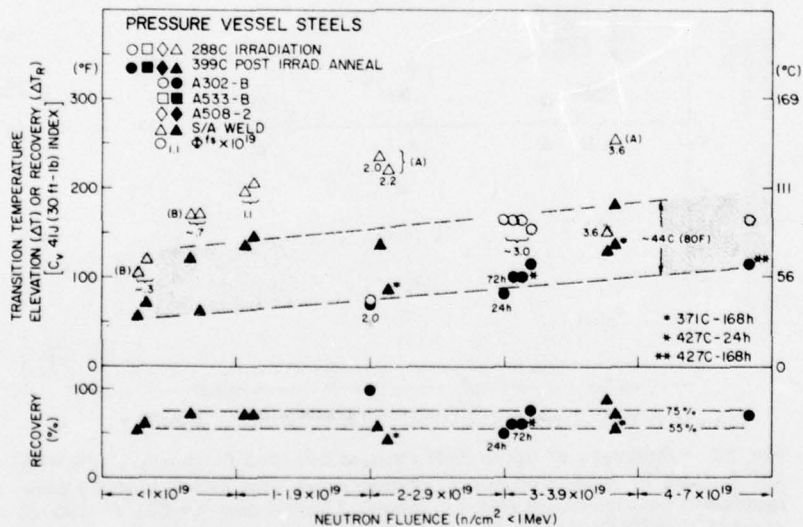


Fig. 20 — Summary of transition-temperature changes (41-J index) observed for several steels with 288°C (550°F) irradiation (open symbols) and with 399°C (750°F) postirradiation heat treatment (filled symbols). Limited data for 371°C (700°F) and 427°C (800°F) annealing are also shown.

HAWTHORNE

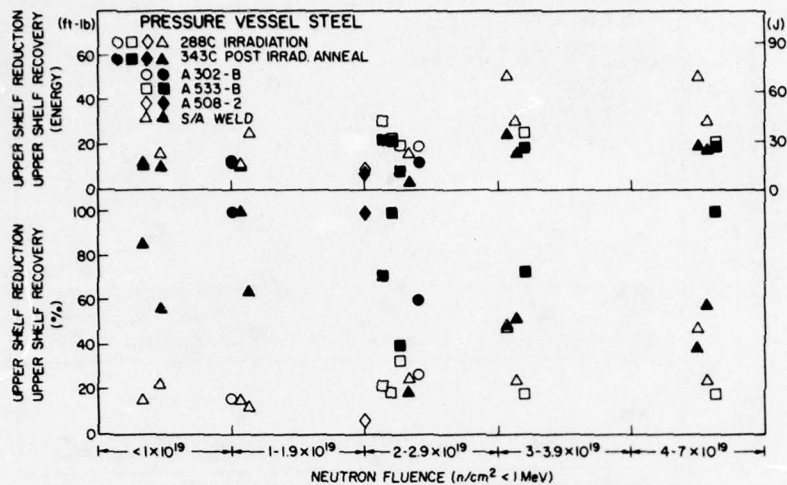


Fig. 21 - Summary of Charpy-V upper-shelf changes observed for several steels with 288°C (550°F) irradiation (open symbols) and with 343°C (650°F) postirradiation heat treatment (filled symbols)

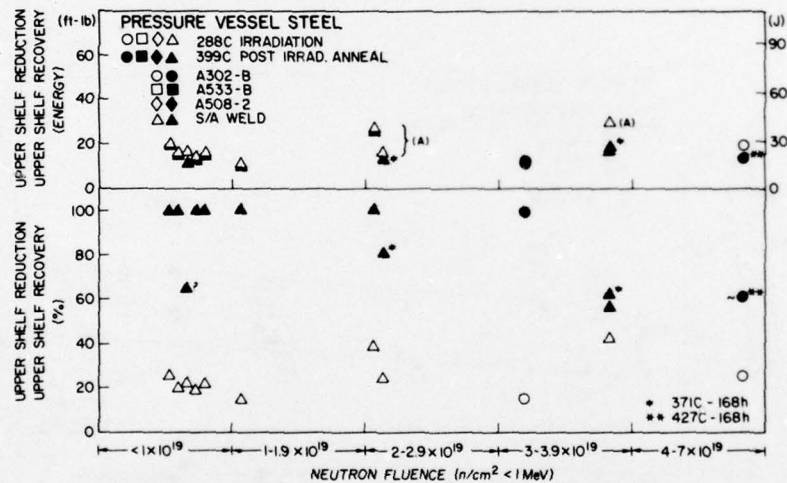


Fig. 22 - Summary of upper-shelf changes observed for several steels with 288°C (550°F) irradiation (open symbols) and with 399°C (750°F) post-irradiation heat treatment (filled symbols). Limited data for 371°C (700°F) and 427°C (800°F) annealing are also shown.

NRL REPORT 8287

Table 2a — Data Compilation (Metric Units) for Notch Ductility Recovery by Postirradiation Heat Treatment

Code No.	Upper Shelf Energy (J)	Fluence ( $10^{19}$ n/cm <sup>2</sup> > 1 MeV)	Irradiation Effects			Annual (°C-hr)	Annealing Recovery				US (%)	Experiment Number
			$\Delta T_{41}$ (°C)	$\Delta T_{48}$ (°C)	$\Delta US$ (J)		$\Delta T_{41}$ (°C)	$\Delta T_{41}$ (%)	$\Delta T_{48}$ (°C)	$\Delta US$ (J)		
A302-B (Plate) (ASTM Reference)												
D36	118	3.0	92	89	43	399-24 399-72 427-24	44 56 56	49 61 61	44 53 —	$\approx 7$ — — <sup>b</sup>	$\approx 16$ — —	L <sup>c</sup> (C18)13 L(C18)13 L(C18)13
F23	111	1.1	78	81	18	343-168	28	36	17	18	100	L(C57)88
F26	98	3.1	86	78	12	399-168	$\approx 64$	$\approx 74$	$\approx 42$	$\approx 7$	$\approx 56$	L(C56)64
F23	106	7.1 (307°C) <sup>c</sup>	92	83	27	427-168	64	70	61	16	60	BRPR <sup>d</sup> -1 (122-3)
D36	118	1.4 (254°C)	111	111	49	316-24	31	28	39	$\approx 8$	$\approx 17$	L(C55)31
F23	111	1.0 (260°C)	100	92	22	343-168	50	50	28	$\approx 22$	$\approx 100$	L(C57)88
D36	118	3.0 (338°C)	61	58	39	427-24	39	64	33	—	—	L(C18)13
F26	98	1.7 (371°C)	17	22	12	454-168	$\approx 17$	$\approx 100$	$\approx 22$	$\approx 12$	$\approx 100$	L(C18)42
A302-B (Plate)												
MBU	172	2.0	42	56	29	399-168	$\approx 42$	100	56	—	—	T <sup>e</sup> (C3)68
40C	102	2.0	72	83	27	343-168 371-168	$\approx 22$ —	$\approx 31$ —	$\approx 31$ —	16 19	60 70	B <sup>f</sup> (B4)-2 B(B4)-2
A533-B (Plate)												
1T	81	2.0	89	—	27	343-168 371-168	$\approx 60$ —	$\approx 38$ —	— —	11 27	18 100	B(B4)-2 B(B4)-2
Q98	189	2.7	117	114	42	343-168 343-336	44 44	38 38	33 —	30 —	71 —	T(D3)74 T(D3)74
CEP1	156	2.1	81	103	30	343-168	31	38	33	30	100	T(D3)75
		6.7	117	108	29	343-168	28	24	17	27	$\approx 100$	T(B3)76
CEP2	190	3.7	92	92	35	343-168	17	18	11	26	73	T(D3)75
N27	186	2.5	78	86	24	343-168 371-168	— —	— —	$\approx 50$ 78	24 27	100 100	B(B4)-2 B(B4)-2
N27	186	2.3 (260°C)	81	92	34	343-168	$\approx 36$	$\approx 45$	53	—	—	T(A4)64
N27	186	2.6 (227°C)	167	153	45	343-168	$\approx 122$	$\approx 73$	$\approx 106$	—	—	T(A4)64
N29	196	2.3 (260°C)	28	28	12	343-168	$\approx 11$	$\approx 40$	11	—	—	T(A4)64
N29	196	2.6 (227°C)	103	114	34	343-168	$\approx 78$	$\approx 76$	89	—	—	T(A4)64
A533-B (Weld)												
Q96	210	2.7	61	72	61	343-168	$\approx 11$	$\approx 18$	11	$\approx 30$	$\approx 49$	T(D3)74
CEW1	145	3.4	175	189	69	343-168	47	27	56	34	49	T(D3)75
		6.1	194	208	69	343-168	56	29	56	27	39	T(B3)76
CEW2	175	3.4	53	75	42	343-168	14	26	13	22	$\approx 52$	T(D3)75
		6.1	69	97	42	343-168	$\approx 17$	$\approx 24$	$\approx 39$	$\approx 24$	$\approx 58$	T(D3)76
W	88	2.2	122	—	22	343-168 371-168	11 47	9 39	$\approx 17$ $\approx 39$	4 18	19 81	B(B4)-2 B(B4)-2
W	94	2.0	131	—	37	399-168	75	57	—	37	100	B(B4)-6
W	94	$\approx 3.6$	142	—	39	399-168	100	71	—	$\approx 23$	$\approx 59$	T(D3)78
						371-168	$\approx 75$	$\approx 53$	—	$\approx 11$	$\approx 63$	T(D3)78
N8	78	$\approx 0.3$	72	69	16	343-168	42	58	—	$\approx 14$	$\approx 100$	B(C2)17
		$\approx 0.7$	100	92	27	399-168	—	—	—	$\approx 30$	$\approx 100$	B(C2)20
AW	163	$\approx 3.6$	$\approx 83$	$\approx 92$	24	399-168 343-168	72 36	87 43	81 36	— —	— —	T(D3)78 T(D3)78
N6	107	1.3	111	100	30	343-168	—	—	—	11	100	B(C2)14
V84	144	1.1	114	119	34	343-168 343-336 399-168	33 33 51	29 29 71	31 31 89	22 26 34	64 76 100	B(B4)10 B(B4)10 B(B4)10
V86	98	1.1	108	117	15	343-168 343-336 399-168	25 25 75	23 23 69	50 50 89	15 15 24	100 100 100	B(B4)10 B(B4)10 B(B4)10
N1	107	$\approx 0.3$	42	78	4	399-168	$\approx 42$	$\approx 100$	78	—	—	B(C2)17
N2	104	$\approx 0.3$	58	56	14	399-168	31	52	33	81	—	B(C2)17
		$\approx 0.7$	94	89	23	399-168	67	71	—	$\approx 15$	$\approx 65$	B(C2)20
N3	100	$\approx 0.3$	67	67	4	399-168	$\approx 39$	$\approx 58$	—	—	—	B(C2)17
		$\approx 0.7$	94	94	19	399-168	33	35	—	$\approx 31$	$\approx 100$	B(C2)20
N4	98	$\approx 0.3$	44	28	8	343-168	28	63	8	41	—	B(C2)17
		$\approx 0.7$	69	58	22	343-168	—	—	—	$\approx 12$	$\approx 56$	B(C2)20
N7	111	$\approx 0.3$	39	42	5	399-168	$\approx 8$	$\approx 21$	42	22	100	B(C2)20
		$\approx 0.7$	69	72	22	399-168	—	—	—	—	100	B(C2)17
A508-2 (Forging)												
Q41	218	2.2	22	25	12	343-168	$\approx 11$	$\approx 50$	11	$\approx 12$	100	T(D3)72
Q71	186	3.0	69	83	29	343-168	42	60	64	—	—	T(D3)72

<sup>a</sup>Low Intensity Test Reactor (LITR).

<sup>b</sup>Not determined.

<sup>c</sup>307°C irradiation.

<sup>d</sup>Big Rock Point Reactor (BRPR).

<sup>e</sup>Union Carbide Research Reactor (UCRR).

<sup>f</sup>SUNY at Buffalo Reactor (UBR).

HAWTHORNE

Table 2b - Data Compilation (English Units) for Notch Ductility Recovery by Postirradiation Heat Treatment

Code No.	Upper Shelf Energy (ft-lb)	Fluence ( $10^{19}$ n/cm <sup>2</sup> > 1 MeV) <sup>c</sup>	Irradiation Effects			Anneal (°F-hr)	Annealing Recovery				US (%)	Experiment Number
			$\Delta T_{30}^a$ (°F)	$\Delta T_{90}^a$ (°F)	$\Delta US$ (ft-lb)		$\Delta T_{30}^a$ (°F)	$\Delta T_{90}^a$ (%)	$\Delta T_{90}^a$ (°F)	$\Delta US$ (ft-lb)		
A302-B (Plate) (ASTM Reference)												
D36	87	3.0	165	160	32	750-24 750-72 800-24	80 100 100	49 61 61	80 95 —	≈ 5 — —	≈ 16 — —	L <sup>b</sup> (C18)13 L(C18)13 L(C18)13
F23	82	1.1	140	145	13	650-168	50	36	30	13	100	L(C57)88
F26	72	3.1	155	140	9	750-168	≈ 115	≈ 74	≈ 75	≈ 5	≈ 56	L(C55)54
F23	78	7.1 (585°F) <sup>c</sup>	165	150	20	800-168	115	70	110	≈ 12	≈ 60	BRPR <sup>d</sup> -1 (122-3)
D36	87	1.4 (490°F)	200	200	36	600-24	55	28	70	≈ 6	≈ 17	L(C55)31
F23	82	1.0 (500°F)	180	165	16	650-168	90	50	50	≈ 16	≈ 100	L(C57)88
D36	87	3.0 (640°F)	110	105	29	800-24	70	64	60	—	—	L(C18)13
D36	87	3.0 (740°F)	65	65	25	900-24	≈ 55	≈ 85	—	—	—	L(C18)13
F26	72	1.7 (700°F)	30	40	9	850-168	≈ 30	≈ 100	≈ 40	≈ 9	≈ 100	L(C18)42
A302-B (Plate)												
MBU	127	2.0	75	100	21	750-168	75	100	100	—	—	T <sup>e</sup> (C3)55
40C	75	2.0	130	150	20	650-168 700-168	≈ 40 —	≈ 31 —	≈ 55 —	12 14	60 70	B <sup>f</sup> (B4)-2 B(B4)-2
A533-B (Plate)												
1T	60	2.0	160	—	20	650-168 700-168	≈ 60 —	≈ 38 —	— —	8 20	18 100	B(B4)-2 B(B4)-2
Q98	139	2.7	205	210	31	650-168 650-336	80 80	38 38	60 —	22 —	71 —	T(D3)74 T(D3)74
CEP1	115	2.1	145	185	22	650-168	55	38	60	22	≈ 100	T(D3)75
		6.7	210	195	21	650-168	50	24	30	20	100	T(B3)76
CEP2	110	3.7	165	165	26	650-168	30	18	20	19	73	T(D3)75
N27	137	2.5	≈ 140	155	18	650-168 700-168	— —	— —	≈ 90 140	18 20	100 100	B(B4)-2 B(B4)-2
N27	137	2.3 (500°F)	145	165	25	650-168	≈ 65	≈ 45	95	—	—	T(A4)64
N27	137	2.6 (440°F)	300	275	33	650-168	≈ 220	≈ 73	≈ 190	—	—	T(A4)64
N29	145	2.3 (500°F)	50	50	9	650-168	≈ 20	≈ 40	≈ 20	—	—	T(A4)64
N29	145	2.6 (440°F)	185	205	25	650-168	≈ 140	≈ 76	160	—	—	T(A4)64
A533-B (Weld)												
Q96	155	2.7	110	130	45	650-168	< 20	≈ 18	20	22	49	T(D3)74
CEW1	107	3.4	315	340	51	650-168	85	27	100	25	49	T(D3)75
		6.1	350	375	51	650-168	100	29	100	20	39	T(B3)76
CEW2	129	3.4	95	135	31	650-168	25	26	23	16	52	T(D3)75
		6.1	125	175	31	650-168	≈ 30	≈ 24	≈ 70	≈ 18	≈ 58	T(B3)76
W	65	2.2	220	—	16	650-168 700-168	20 85	9 39	≈ 30 ≈ 70	3 13	3 81	B(B4)-2 B(B4)-2
W	69	2.0	235	—	27	750-168	135	57	—	27	100	B(B4)-6
W	69	3.6	255	—	29	750-168 700-168	180 ≈ 135	71 ≈ 53	— —	≈ 17 ≈ 19	≈ 59 ≈ 63	T(D3)-78 T(D3)-78
N8	78	≈ 0.3	130	125	12	650-168	75	58	—	≈ 10	≈ 100	B(C2)17
		≈ 0.7	180	165	20	750-168	—	—	—	≈ 22	≈ 100	B(C2)20
AW	120	≈ 3.6	≈ 150	≈ 165	18	650-168 750-168	65 130	43 87	65 145	— —	— —	T(D3)78 T(D3)78
N6	79	1.3	200	180	22	650-168	—	—	22	100	—	B(C2)14
V84	106	1.1	205	215	25	650-168 650-336	60 60	29 29	55 55	16 19	64 76	B(B4)10 B(B4)10
		1.1	195	210	11	750-168 650-336	145 45	71 23	160 90	25 11	100 100	B(B4)10 B(B4)10
		1.1	195	210	11	750-168	135	69	160	18	100	B(B4)10
N1	79	≈ 0.3	75	140	3	750-168	≈ 75	≈ 100	140	—	—	B(C2)17
N2	77	≈ 0.3	105	100	10	750-168	55	52	60	60	—	B(C2)17
		≈ 0.7	170	160	17	750-168	120	71	—	≈ 11	> 65	B(C2)20
N3	74	≈ 0.3	120	120	3	750-168	≈ 70	≈ 58	—	—	—	B(C2)17
		≈ 0.7	170	170	14	750-168	60	35	—	≈ 23	≈ 100	B(C2)20
N4	72	≈ 0.3	80	50	6	650-168	50	63	15	30	—	B(C2)17
		≈ 0.7	125	105	16	650-168	—	—	—	≈ 9	≈ 56	B(C2)20
		≈ 0.3	70	75	4	750-168	—	—	—	16	100	B(C2)20
N7	82	≈ 0.7	130	130	16	750-168	≈ 15	≈ 21	75	—	—	B(C2)17
		≈ 0.7	130	130	16	750-168	—	—	—	26	100	B(C2)20
A508-2 (Forging)												
Q41	161	2.2	40	45	9	650-168	≈ 20	≈ 50	20	≈ 9	100	T(D3)72
Q71	137	3.0	125	150	21	650-168	75	60	115	—	—	T(D3)72

<sup>a</sup>Low Intensity Test Reactor (LITR).

<sup>b</sup>Not determined.

<sup>c</sup>585°C irradiation.

<sup>d</sup>Big Rock Point Reactor (BRPR).

<sup>e</sup>Union Carbide Research Reactor (UCRR).

<sup>f</sup>SUNY at Buffalo Reactor (UBR).

Table 3 — Chemical Compositions of Survey Materials (Plate, Forging, Weld Deposit)

MATERIAL	Chemical Composition (wt-%)									
	CODE	Cu	P	C	Mn	S	Si	Ni	Cr	Mo
A302-B (Plate) (ASTM Ref)	D36	0.20	0.011	0.24	1.34	0.023	0.23	0.18	0.11	0.51
	F23	0.20	0.011	0.24	1.34	0.023	0.23	0.18	0.11	0.51
	F26	0.20	0.011	0.24	1.34	0.023	0.23	0.18	0.11	0.51
A302-B (Plate)	MBU	0.15	0.006	0.25	1.37	0.011	0.21	0.26	0.11	0.63
	40C	0.008	0.021	0.23	1.30	0.022	0.21	—	—	0.53
A533-B (Plate)	1T	0.24	0.012	0.22	1.30	0.024	0.28	0.52	—	0.40
	Q98	0.22	0.006	0.25	1.44	0.010	0.23	0.58	0.12	0.52
	CEP1	0.17	0.009	0.23	1.29	0.015	0.21	0.56	0.10	0.57
	CEP2	0.24	0.008	0.25	1.40	0.011	0.23	0.62	0.11	0.59
	N27	0.13	0.008	0.17	1.22	0.008	0.19	0.58	—	0.50
	N29	0.03	0.008	0.17	1.21	0.007	0.20	0.56	—	0.50
A533-B* (Weld)	Q96	0.26	0.010	0.17	1.17	0.010	0.18	0.18	0.08	0.51
	CEW1	0.36	0.015	0.14	1.35	0.012	0.22	0.78	0.07	0.55
	CEW2	0.20	0.016	0.13	1.11	0.013	0.17	0.04	0.05	0.55
	W	0.35	0.020	0.09	1.45	0.013	0.68	0.57	—	0.39
	AW	0.055	0.022	0.11	1.33	0.012	0.44	0.97	0.07	0.54
	V84	0.35	0.013	0.14	1.56	0.011	0.14	0.62	0.03	0.53
	V86	0.35	0.016	0.08	1.60	0.013	0.55	0.69	—	0.40
A508-2 (Forging)	Q41	0.09	0.005	0.21	0.68	0.008	0.27	0.71	0.39	0.59
	Q71	0.13	0.007	0.19	0.69	0.009	0.31	0.82	0.38	0.62

\*Chemical compositions of welds N1 to N8 are not available.

## SUMMARY

Reactor pressure-vessel steels including A302-B, A533-B, A508-2, and companion weld metals exhibit significant variability in their response to postirradiation heat treatment for embrittlement relief. Also, a difference in response to postirradiation heat treatment has been observed between transition-temperature and upper-shelf-energy  $C_v$  properties for a given material.

Several metallurgical and service factors are suspected of contributing to the variation in notch ductility recovery and are identified. Within the limitations of the existing experimental data, the contributions or importance of certain of these factors could be assessed using direct or indirect test comparisons. Table 4 identifies where assessments were permitted by the data and the qualification made in each case. Among those variables identified as contributing factors, annealing temperature and duration are ranked as having the greatest influence on the recovery of properties. This relationship is in turn reflected in the importance of heat-treatment time and conditions selected for cyclic annealing and reirradiation treatments. Impurity-element composition (copper content) is ranked second in importance. Here a detrimental effect of a high copper content (0.30% Cu) on upper-shelf recovery was demonstrated for A302-B steel. A similar effect for companion weld deposits is quite probable. Of those factors yet to be qualified, four should be given first priority. The significance of relative radiation resistance and of alloying-element composition should be established to preclude possible technical surprises in future annealing operations. Annealing recovery with different first-cycle fluences and second-cycle fluences (repeat irradiation) should be evaluated to help establish optimum heat treatment schedules which provide maximum benefit and flexibility.

The present data show that 343°C annealing does not have high promise for those reactor applications having first-cycle fluences exceeding  $1 \times 10^{19}$  n/cm<sup>2</sup> > 1 MeV. On the other hand, it is clear that 399°C annealing or annealing at somewhat higher temperatures does have significant promise for the embrittlement relief of reactor vessels. With this heat treatment, transition-temperature recoveries of about 55% minimum and 75% maximum can be expected for most materials, based on the data survey. More importantly, full upper-shelf recovery for fluences up to  $3 \times 10^{19}$  n/cm<sup>2</sup> appears typical for the materials of concern.

Although major progress has been made, the present state of the art is insufficiently advanced to permit an immediate consideration of the annealing method for the relief of reactor vessel embrittlement. One basis for this opinion is that experimental data describing property changes with reirradiation are too sparse to confidently base engineering judgments and property projections for this condition. An equally important basis is that knowledge of factors governing reirradiation behavior (sensitivity) is extremely limited. To compound both issues, it has been established that the rate of reembrittlement of annealed material is significantly different (greater) from that of nonannealed material at an equivalent fluence level. The trend in upper-shelf reduction with reirradiation likewise appears to be significantly different from that of nonannealed material. Beyond first-cycle behavior, information on notch ductility trends with multiple annealing and reirradiation cycles is in comparison practically nonexistent. Thus, although high-temperature annealing shows promise for embrittlement relief, further research must precede its application. Specifically, further research is needed on single-cycle and multicycle annealing and reirradiation treatments. For maximum

Table 4 — Status of Experimental Assessments of Variables Suspected of Contributing to the Alleviation of Radiation Embrittlement by Postirradiation Annealing

Variable Description	Experimental Qualification		
	Contributing	Noncontributing	Not Established
Irradiation temperature	X		
Neutron fluence	X <sup>a</sup>		
Relative radiation resistance			X
Applied Stress: During irradiation During annealing		X	X
Impurity element composition	X		
Alloying element composition			X
Product form			X
Annealing temperature	X		
Annealing duration	X		
Cyclic anneal conditions (temp., time)	X		
Fluence before first anneal			X
Fluence between anneals			X

<sup>a</sup>Dependent on the heat treatment condition.

## HAWTHORNE

usefulness the investigations should concentrate largely on 399°C heat treatments rather than 343°C heat treatments. Concurrently, in-depth studies of the capabilities of the high-temperature annealing option should be verified for the single-cycle irradiation and anneal condition for all projected material, fluence, and service parameters.

### ACKNOWLEDGMENTS

This study was sponsored by the U.S. Nuclear Regulatory Commission (NRC), Reactor Safety Research Division, Metallurgy and Materials Branch, and Operating Reactors Division, Materials Engineering Branch.

### REFERENCES

1. ASME Boiler and Pressure Vessel Code, Sec. III, Subsection NB (Class 1 Components), NB-2331, American Society of Mechanical Engineers, New York, 1974.
2. "Fracture Toughness and Surveillance Program Requirements," Appendixes G and H, Title 10, Code of Federal Regulations, Part 50 (10 CFR Part 50), U.S. Atomic Energy Commission, Federal Register 38, 136 (17 July 1973).
3. "Effects of Residual Elements on Predicted Radiation Damage to Reactor Vessel Materials," Regulatory Guide 1.99, U.S. Nuclear Regulatory Commission, Office of Standards Development, Washington, D.C., Apr. 1977.
4. J.R. Hawthorne, H.E. Watson, and F.J. Loss, "Exploratory Investigations of Cyclic Irradiation and Annealing Effects on Notch Ductility of A533-B Weld Deposits," Symposium on Effects of Radiation on Structural Materials, ASTM, Richland, Wash., July 1978.
5. T.U. Marston and K.E. Stahlkopf, "Radiation Damage and Mitigation Research at EPRI," Joint ASME/CSME Pressure Vessels and Piping Conference, Montreal, Canada, 25-30 June 1978.
6. T.R. Mager and T.U. Marston, "A Description of a Study for the Thermal Anneal of Neutron-Embrittled Reactor Vessel Materials," Joint ASME/CSME Pressure Vessels and Piping Conference, Montreal, Canada, 25-30 June 1978.
7. E.N. Klausnitzer, A. Gerscha, and C. Leitz, "Irradiation Behaviour of NiCrMo Weld Metal," Symposium on Effects of Radiation on Structural Materials," ASTM, Richland, Wash., July 1978.
8. U. Potapovs, G.W. Knighton, and A.S. Denton, "Critique of In-Place Annealing of SM-1A Nuclear Reactor Vessel," Nuclear Engineering and Design 8, 39-57 (1968).
9. U. Potapovs, J.R. Hawthorne, and C.Z. Serpan, Jr., "Notch Ductility Properties of SM-1A Reactor Pressure Vessel Following the In-Place Annealing Operation," Nuclear Applications 5, 389-409 (Dec. 1968).
10. J.R. Hawthorne, "Radiation Effects Information Generated on the ASTM Reference Correlation-Monitor Steels," ASTM DS-54, American Society for Testing and Materials, Philadelphia, July 1974.

NRL REPORT 8287

11. J.R. Hawthorne, C.Z. Serpan, H.E. Watson, and R.A. Gray, "Irradiation Effects on Reactor Structural Materials, QPR, 1 Nov 1966-31 Jan 1967," NRL Memorandum Report 1753, 15 Feb. 1967.
12. J.R. Hawthorne, "Further Observations on A533-B Steel Plate Tailored for Improved Radiation Embrittlement Resistance," NRL Report 7917, 22 Sept. 1975.
13. J.R. Hawthorne, J.J. Koziol, and R.C. Groeschel, "Evaluation of Commercial Production A533-B Plates and Weld Deposits Tailored for Improved Radiation Embrittlement Resistance," pp. 83-102 in *Properties of Reactor Structural Alloys After Neutron or Particle Irradiation*, ASTM STP 570, Feb. 1976.
14. J.R. Hawthorne, "Significance of Copper, Phosphorus, and Sulfur Content to Radiation Sensitivity and Postirradiation Heat Treatment of A302-B Steel," NRL Report 8264, Oct. 1978, and NUREG/CR-0327, U.S. Nuclear Regulatory Commission.
15. J.R. Hawthorne and F.J. Loss, "The Effects of Coupling Nuclear Radiation With Static and Cyclic Service Stresses and of Periodic Proof Testing on Pressure Vessel Material Behavior," NRL Report 6620, 1 Aug. 1967.
16. U. Potapovs and J.R. Hawthorne, "The Effect of Residual Elements on 550° F Irradiation Response of Selected Pressure Vessel Steels and Weldments," NRL Report 6803, 22 Nov. 1968, and Nuclear Applications 6 (No. 1), 27-46 (Jan. 1969).
17. J.R. Hawthorne, J.J. Koziol, and S.T. Byrne, "Evaluation of Commercial Production A533-B Steel Plates and Weld Deposits with Extra-Low Copper Content for Radiation Resistance," Symposium on Effects of Radiation on Structural Materials, ASTM, Richland, Wash., July 1978.