


AD-A071 157

ENGELHARD MINERALS AND CHEMICALS CORP EDISON N J RES--ETC F/G 10/2  
DESIGN AND DEVELOPMENT OF A 30 WATT SOLID POLYMER ELECTROLYTE F--ETC(U)  
DEC 78 O ADLHART DAAK70-77-C-0222

UNCLASSIFIED

| OF |  
AD  
A071157

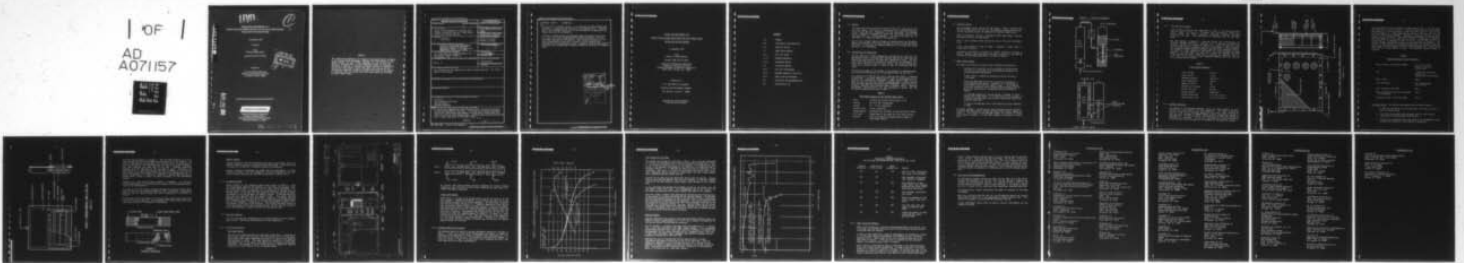

END

DATE

FILMED

8-79

DDC

**LEVEL II**

*P*

**DESIGN AND DEVELOPMENT OF A  
30 WATT SOLID POLYMER ELECTROLYTE FUEL CELL POWER SOURCE  
FUELED WITH CALCIUM HYDRIDE**

*R*

12 December 1978

O. Adlhart

Final  
Technical Program Report

Contract DAAK 70-77-C-0222

DDC  
RECEIVED  
JUN 26 1979  
C

Prepared for

U. S. Army Mobility Equipment  
Research and Development Command  
Fort Belvoir, Virginia 22060

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED.

**ENGELHARD**

Research & Development Department  
Engelhard Industries Division  
Engelhard Minerals & Chemicals Corporation  
Menlo Park, Edison, N. J. 08817

79 06 21 004

201120A

DDC FILE COPY

**NOTICE**

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States nor any agency thereof, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for any third party's use or the results of such use of any information, apparatus, product or process disclosed in this report or represents that its use by such third party would not infringe privately owned rights.

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle)		5. TYPE OF REPORT & PERIOD COVERED
6. Design and Development of a 30 Watt Solid Polymer Electrolyte Fuel Cell Power Source Fueled with Calcium Hydride		Final Technical Program Report.
7. AUTHOR(s)		6. PERFORMING ORG. REPORT NUMBER
10. O./Adlhart		Accession No. 003136
9. PERFORMING ORGANIZATION NAME AND ADDRESS		8. CONTRACT OR GRANT NUMBER(s)
Research & Development Department Engelhard Industries Division Engelhard Minerals & Chemicals Corp. Menlo Park, Edison, N.J. 08817		15. DAAK70-77-C-0222
11. CONTROLLING OFFICE NAME AND ADDRESS		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
U.S. Army Mobility Equipment Research and Development Command, DRDME-EC, Fort Belvoir, Va.		12. 26p.
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE
Same as 11		11. 12 Dec 1978
		13. NUMBER OF PAGES
		15. SECURITY CLASS. (of this report)
		Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report)		
This document has been approved for public release and sale. Its distribution is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)		
Fuel Cells Solid Polymer Electrolyte Calcium Hydride Hydrogen Generator		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)		
In recent years MERDCOM has shown renewed interest in the Solid Polymer Electrolyte Hydrogen-Air Fuel Cell. It focuses on the broad spectrum of applications where power requirements are quite small ranging from fractions of a watt to a few hundred watts. Handling simplicity and versatility are of utmost importance in this power range. →		
(cont'd)		

403676

ABSTRACT CONT'D (BLOCK 20)

The SPE cell is uniquely suited. It is operative at about ambient temperatures, is rugged and has excellent life characteristics. Combined with a solid hydrogen source such as calcium hydride or magnesium high energy densities are attainable.

A 24 Volt, 30 Watt device was developed under the contract consisting of a static SPE stack integrated with a hydrogen generator utilizing cartridge contained calcium hydride. Even in short missions of a few hours energy densities are well in excess of those obtained with secondary batteries. Additional work is needed to optimize the system for operation over a broad range of ambient conditions including low temperatures.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	<i>data on file</i>
By	<i>no proprietary notice</i>
Distribution/	<i>NO</i>
Availability Codes	
Dist	Avail and/or special
<i>A</i>	

**ENGELHARD**

Design and Development of a  
30 Watt Solid Polymer Electrolyte Fuel Cell Power Source  
Fueled with Calcium Hydride

12 December 1978

Final  
Technical Program Report

Contract DAAK 70-77-C-0222

Research & Development Department  
Engelhard Industries Division  
Engelhard Minerals & Chemicals Corporation  
Menlo Park, Edison, N.J. 08817

Prepared for

U.S. Army Mobility Equipment  
Research and Development Command  
Fort Belvoir, Virginia 22060

Approved for Public Release;  
Distribution Unlimited

CONTENTS

1.0	Summary
2.0	Introduction and Objectives
3.0	Technical Effort
3.1	Power Source Design
3.1.1	Fuel Cell Stack
3.1.2	Hydrogen Generator
3.1.3	Integrated System
3.2	Evaluation Results
3.2.1	Fuel Cell Performance
3.2.2	Hydrogen Generator Evaluation
3.2.3	Power Source Performance
4.0	Conclusion and Recommendations
5.0	Distribution List

## 1.0 Summary

The report describes design and evaluation data for a hydrogen-air SPE fuel cell system. The device is integrated with a hydrogen generator using calcium hydride - contained in a fuel cartridge - as hydrogen source. Hydrogen is generated by direct but restricted contact of the fuel with water in a "Kipp" generator. Its flow to the fuel cell is regulated in a "dead end" mode of cell operation.

The 28 volt, 30 watt device provides an energy density of 60 WH/kg. Based on the weight of the fuel cartridge in excess of 1000 WH/kg are delivered. If the water for hydride conversion is included, the energy density is still 550 WH/kg.

## 2.0 Introduction and Objectives

Contract DAAK 70-77-C-0222 represents a continuation of a SPE fuel cell development effort initiated under contract DAAK 53-76-C-0130 with the design and fabrication of 30 three watt hydrogen-air cells. The program proved that bipolar construction features of the phosphoric acid stack can be applied to the SPE stack design. The current program provides for a scale-up from a 3 watt, 5 volt to a 30 watt, 28 volt stack.

An additional aspect of the program is the design of a hydrogen generator using calcium hydride and its integration with the fuel cell.

The combination of the SPE cell with a hydride fuel offers -- compared to batteries -- increased energy density, ease of rechargeability and superior low temperature performance. Under contract DAAK 70-77-C-0222, two 28 volt, 30 watt devices integrated with a calcium hydride based hydrogen generator were delivered to MERADCOM. Two 24 volt units without a generator were supplied under a contract option. Required performance characteristics for the hydrogen-air stacks and the integrated system are outlined in Table 1.

Table 1

Performance Objectives for Hydride Power Source

Power	30 watts at 40-110°F and 20 watts at 0°F
Voltage	24 to 32 VDC, unregulated
Current	0.1 - 1.25 A adjustable
Start-up time	15 min. above 40°F
Energy density	550 WH/kg fuel and water at any load above 3 watts
Tilt angle	Operational at any angle up to 45° from vertical
Mission	4 hrs at 30 watts and proportionally longer at lower power levels

### 3.0 Technical Effort

The development effort consists of two phases. Phase 1 involves the design and fabrication of fuel cell and generator subsystems and their testing separately as well as combined to a complete power source.

Based on evaluation results, a redesign follows under Phase 2 and two deliverable devices are fabricated.

Phase 1 and 2 designs differ materially only in the stack configuration.

A dual stack system is used in Phase 1, whereas a single stack is relied upon on Phase 2.

Information discussed in Section 3.1 refers primarily to Phase 2 design. However, evaluation data discussed in Section 3.2 are derived from testing performed under Phase 1 as well as Phase 2.

### 3.1 Power Source Design

The power source design is based on the following considerations:

Reactant air to the fuel cell is supplied by diffusion and air access is restricted to prevent membrane dehydration at elevated ambient temperatures.

Product water is removed by evaporation and/or drained as liquid water.

Waste heat generated in the fuel cell and by reaction of calcium hydride with water -- combined, it is equivalent to approximately two times the electric output -- is dissipated by natural convection and at elevated ambient temperatures by additional cooling with a thermostatically controlled air blower.


For hydrogen generation, calcium hydride is brought in direct contact with liquid water. It is contained for this purpose in a tubular cartridge with provision for liquid water access and hydroxide expansion.

To control the hydrogen flow a self-regulating "Kipp" generator is used.

A systems schematic indicating the above mentioned design features, including the mode reactant supply and waste heat removal appears in Figure 1. The filter in the hydrogen supply line serves to absorb trace amounts of ammonia. It was later removed as discussed in section 3.2.2.

**ENGELHARD**  
INDUSTRIES

FIGURE 1 - SYSTEMS SCHEMATIC

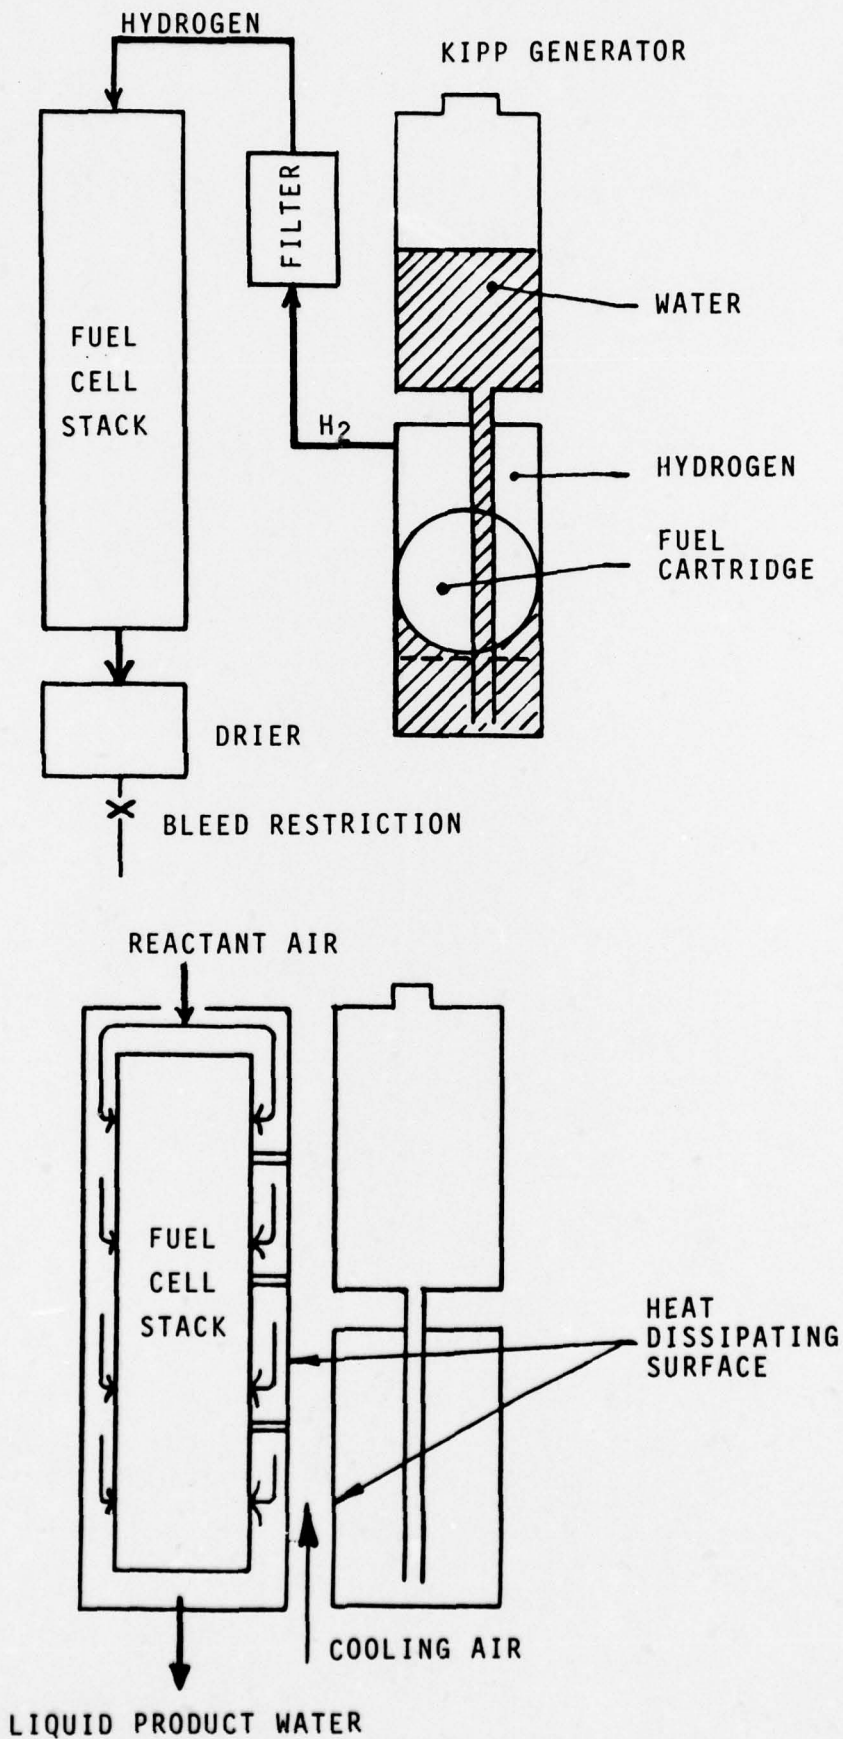

### 3.1.1 Fuel Cell Stack Design

Stack design parameters are summarized in Table 2 and detailed design features appear in Figure 2. A bipolar cell construction, carbon collector plates and carbon substrate supported, platinum activated electrodes are used. The electrodes are laminated with the SPE membrane.

The stack design is based on a long and narrow cell configuration and external hydrogen manifolds. Reactant air is supplied by diffusion. Hydrogen, supplied at a pressure of 5-20 cm W.C., enters one manifold at the stack top and exists the opposite manifold at the bottom. Stack components are assembled between aluminum channels rigidized with honeycomb inserts. The assembly is held together by perforated face plates attached to these channels. The same plates are used also to press the hydrogen manifolds firmly against the stack. Waste heat is rejected by convection from the stack and a heat dissipating plate connected thermally with the stack by five extended bipolar plates.

Table 2

Stack Design Parameters

Stack voltage	24-32 V
Stack current	1.25 A
Hydrogen pressure	<25 cm W.C.
Stack temperature	<125°F
Number of cells	34
Nominal cell voltage	0.70 V
Active cell area	48 cm <sup>2</sup>
Current density	26.mA.cm <sup>-2</sup>
Bipolar plate size	3.1 x 23 x 0.4 cm
Cooling plate size	3.7 x 23 x 0.4 cm

### 3.1.2 Hydrogen Generator

The design of the hydrogen generator relies on direct contact of solid hydride with liquid water in a "Kipp" generator. This mode of operation assures a high rate of hydrogen generation even from a small quantity of fuel and quick response to demand changes without intermediate storage of hydrogen gas. In order to control the reaction with water the hydride is contained in a cartridge. The use of a cartridge also simplifies handling of the moisture sensitive material and disposal of the hydroxide residue.

300 L...G A...

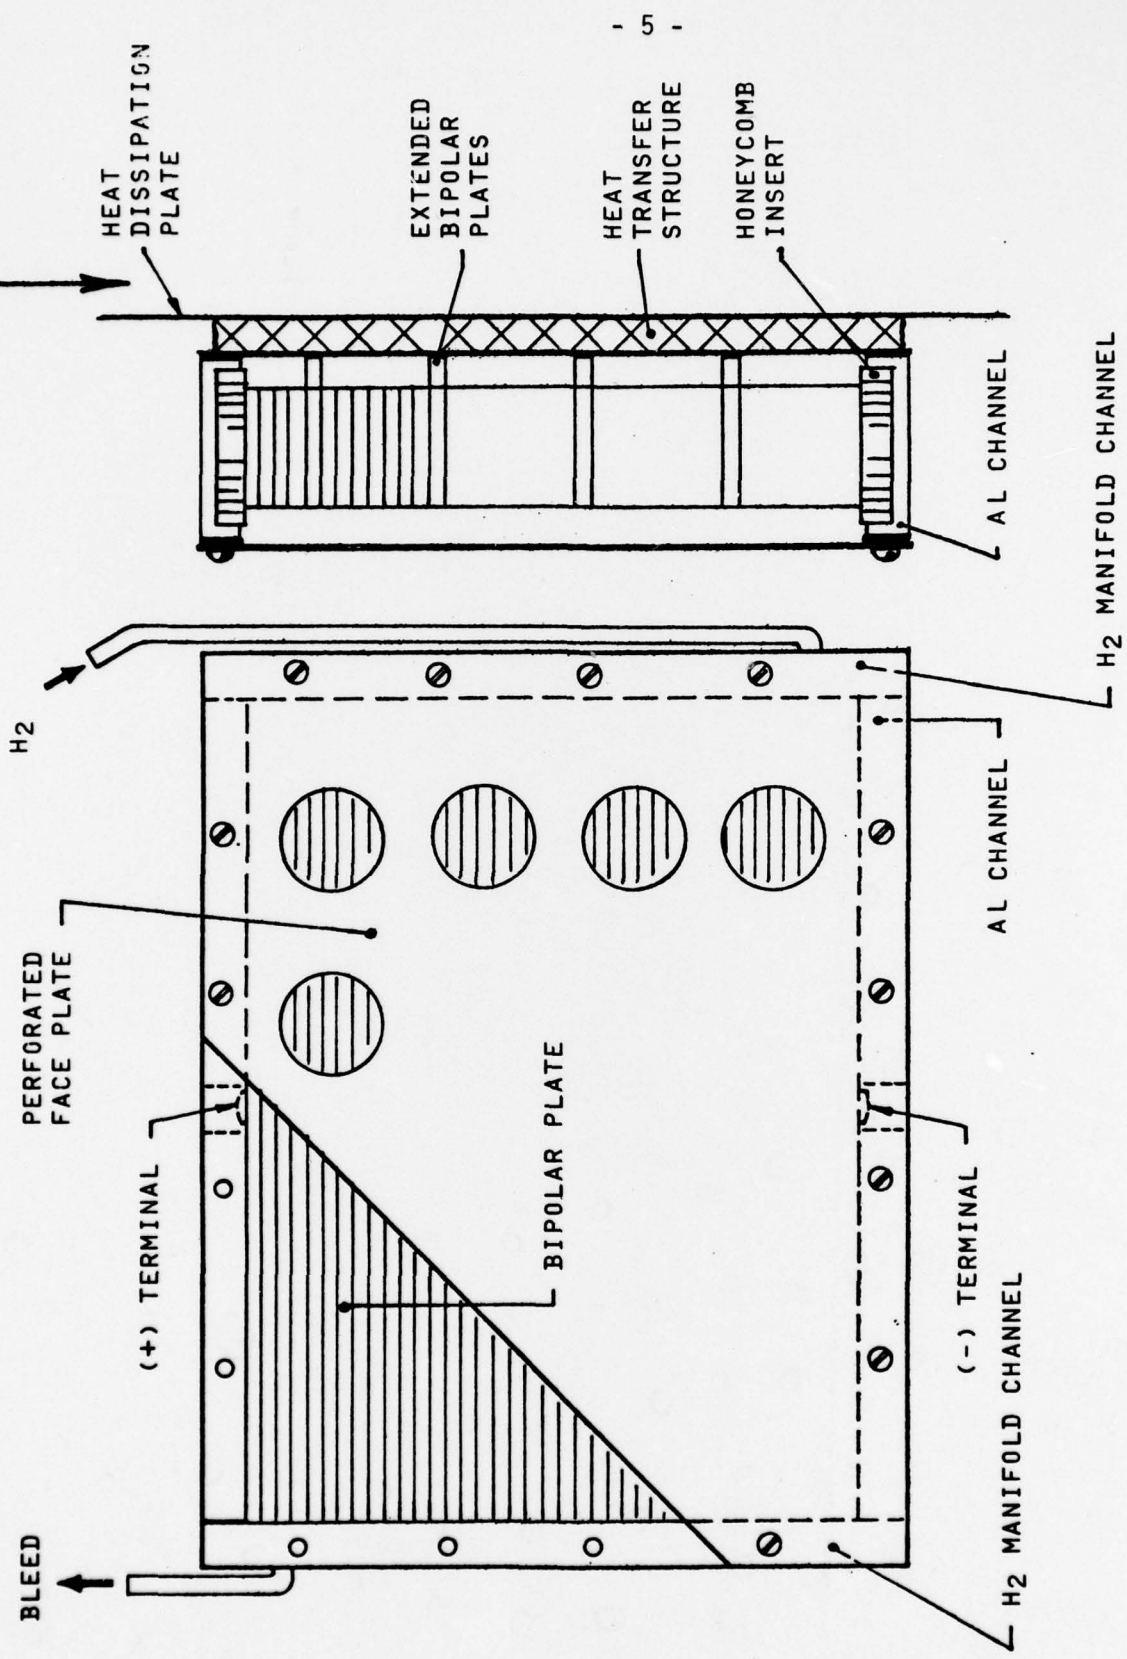


FIGURE 2 - FUEL CELL STACK, FRONT & SIDE VIEW  
(SCALE 1/2)

Design parameters of the generator are summarized in Table 3. The principle components are the water reservoir, reaction chamber and fuel cartridges. The generator is self regulating. Water from the reservoir flows to the reaction chamber via a tube connecting the bottom of the reservoir with the bottom of the reaction chamber. Hydrogen is generated as soon as water reaches the fuel cartridge. The rate of generation depends on the degree of cartridge immersion and is controlled as follows: If hydrogen is generated faster than it is consumed in the fuel cell, pressure increases in the reaction chamber forcing water partly or fully back into the reservoir; conversely, if more hydrogen is consumed than generated, the pressure drops and water flows from the reservoir into the reaction chamber thus immersing the cartridge to a larger degree in water. The generator design is shown in Figure 3.

Table 3

Hydrogen Generator Design Parameters

Water reservoir and reactor chamber	12.5 x 28 x 3.8 cm aluminum container, 1330 ml each
Fuel	-4 mesh calcium hydride >93% purity contains up to 1% nitrogen
Water charge	900 ml
Fuel cartridges	Two aluminum tubes, 3.8 x 25.5 cm
Fuel charge per cartridge	140g
Water consumption upon full conversion (2 cartridges)	470 ml
Expansion volume in each cartridge	120 ml

Cartridge Design: The hydride cartridge has the following features:

1. A container consisting of a thin wall metal tube with a series of holes for water entry.
2. Lining of the container with absorbent material such as glass fiber paper for uniform water distribution.
3. Provision for expansion within the container to accommodate volume changes upon conversion of the hydride to hydroxide.

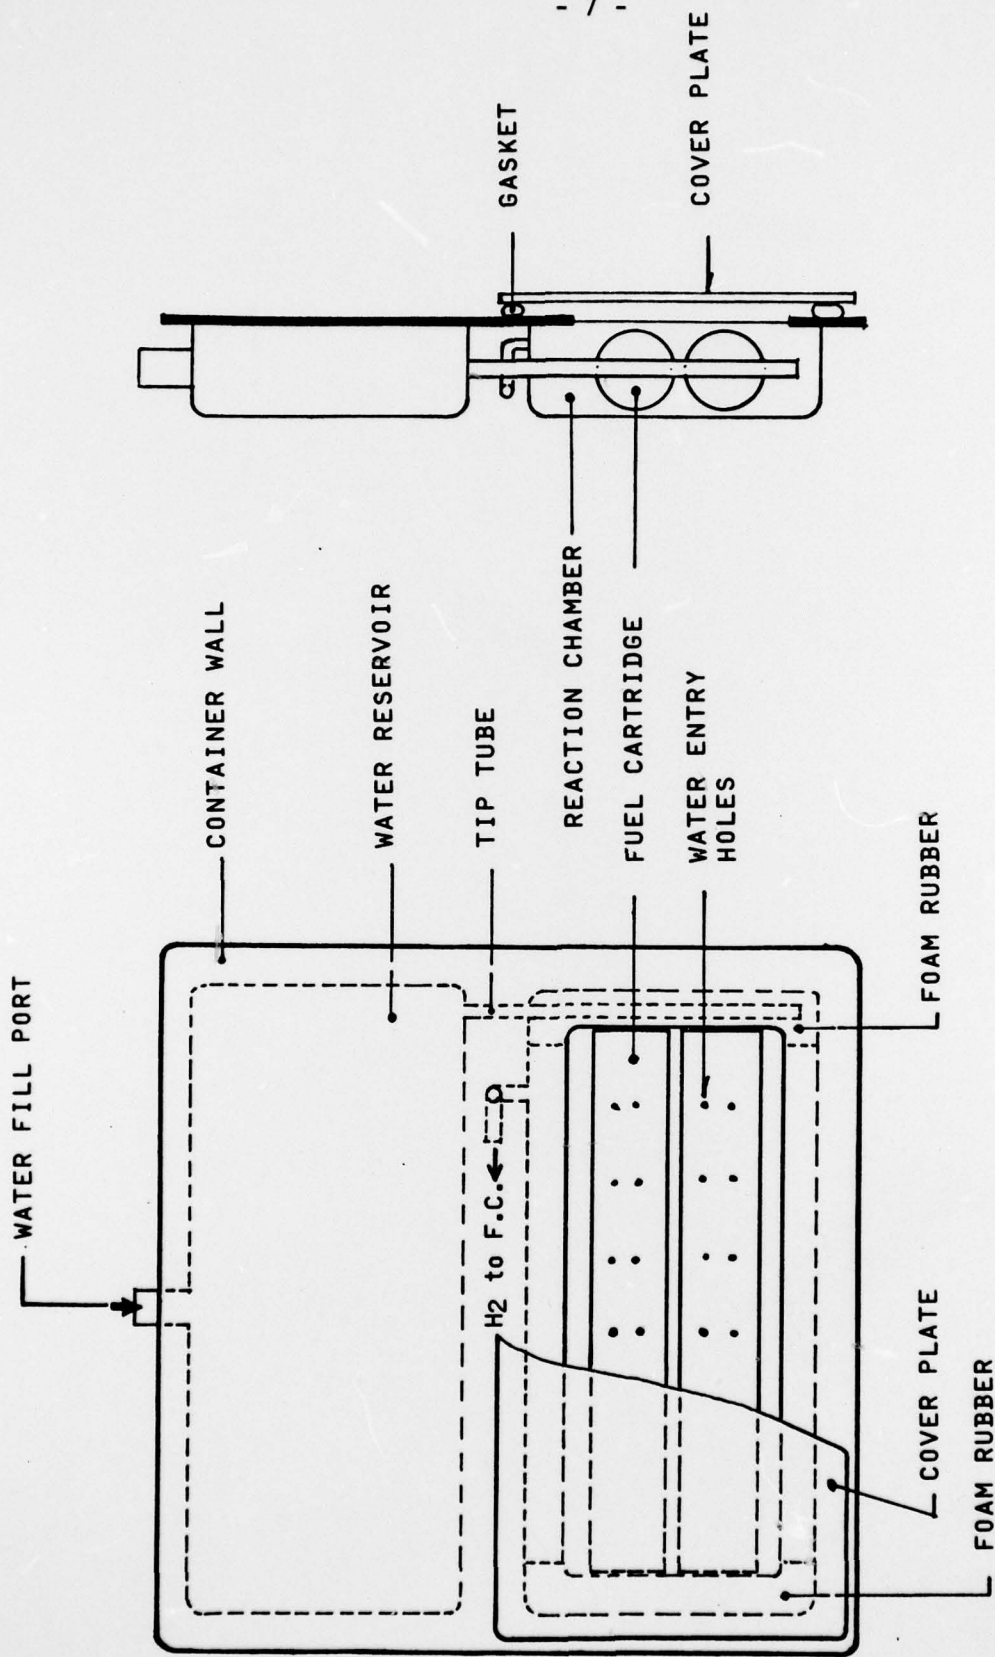


FIGURE 3 - HYDROGEN GENERATOR, FRONT & SIDE VIEW


(SCALE 1/3)

Cartridge design appears in Figure 4. The cartridge consists of a 25 cm long aluminum tube of 3.8 cm diameter with 20 holes of 0.7 mm diameter. The tube is lined with glass fiber paper and filled to 2/3 of its volume with -4 mesh calcium hydride. The remaining space is taken up by plugs of polystyrene foam inserted from both ends of the tube. Hydrogen generation commences with the immersion of the cartridge in water. Initially, the water enters at a rate controlled by the size and number of holes and is distributed by the glass paper lining contacting the hydride bed over its entire circumference. As hydride is converted, a porous hydroxide cake is formed which provides a path for water transport to the unconverted hydride.

Formation of a cake with suitable porosity is important. It very much affects completeness of conversion and the degree to which hydrogen generation rate can be regulated.

If porosity is too low, water transport through the cake may become inadequate to sustain the required generation rate; conversely, if hydroxide particles are too loosely packed, the rate of generation is difficult to control.

The provision for volume expansion in the cartridge assures the formation of a cake with suitable porosity. It accommodates the volume changes that take place upon conversion of the hydride to hydroxide.

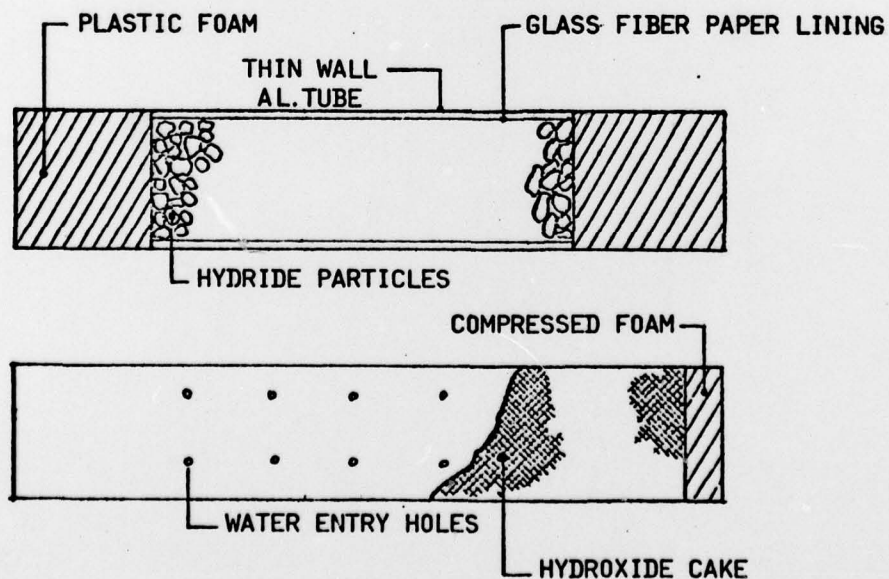

**FIGURE 4**  
**HYDRIDE CARTRIDGE**

### Ammonia Removal

Hydrogen generated from calcium hydride may contain appreciable amounts of ammonia formed by reaction of calcium nitride with water. (Calcium nitride is present as an impurity in technical grade calcium hydride).

Removal of ammonia is necessary for stable long term performance. A filter containing sulfonic acid resin (Amberlyst 15) was considered for this purpose but found unsuitable and modified as described in section 3.2.2.

### 3.1.3. Integrated System

Design features of the integrated power source appear in Figure 5. Fuel cell and hydrogen generator are mounted on 1.5 mm thick, 30 cm square aluminum sheets which make up the wall of the power source container. Air blower, ammonia filter and bleed gas drier are mounted on the same plate as the fuel cell. Filter and drier are accessible from the outside to permit replacement of the drying agent and ammonia scrubber. A flexible hose connects the Kipp generator with the ammonia filter. From there, purified hydrogen enters the cell stack at the top. Bleed gas is released from the stack bottom to the bleed gas drier and from there through a porous metal disc to the atmosphere. Reactant air is supplied through nine holes of 1.6 cm diameter in the top of the container. Air reaches the cells through a .75 cm gap between cell stack and container wall on one side and an 0.6 cm thick perforated heat transfer structure on the opposite side.

## 3.2 Evaluation Results


Fuel cell and generator subsystem were evaluated separately and as complete power source. Testing was performed only at room temperature.

### 3.2.1 Fuel Cell Evaluation


#### Dual Stack Design


The fuel cell system designed and fabricated under Phase 1 consisted of two 34 cell stacks with an active cell area  $20 \text{ cm}^2$  (9.1 x 2.2 cm) each. These stacks were tested connected electrically in parallel and supplied with hydrogen in series. This mode operation resulted in a significant performance decline and uneven load sharing due to thermal and moisture imbalances. The changes in stack voltage and stack temperature observed during a 20 hr test (load  $20 \Omega$ ) are illustrated below:

REVISION DESCRIPTION	

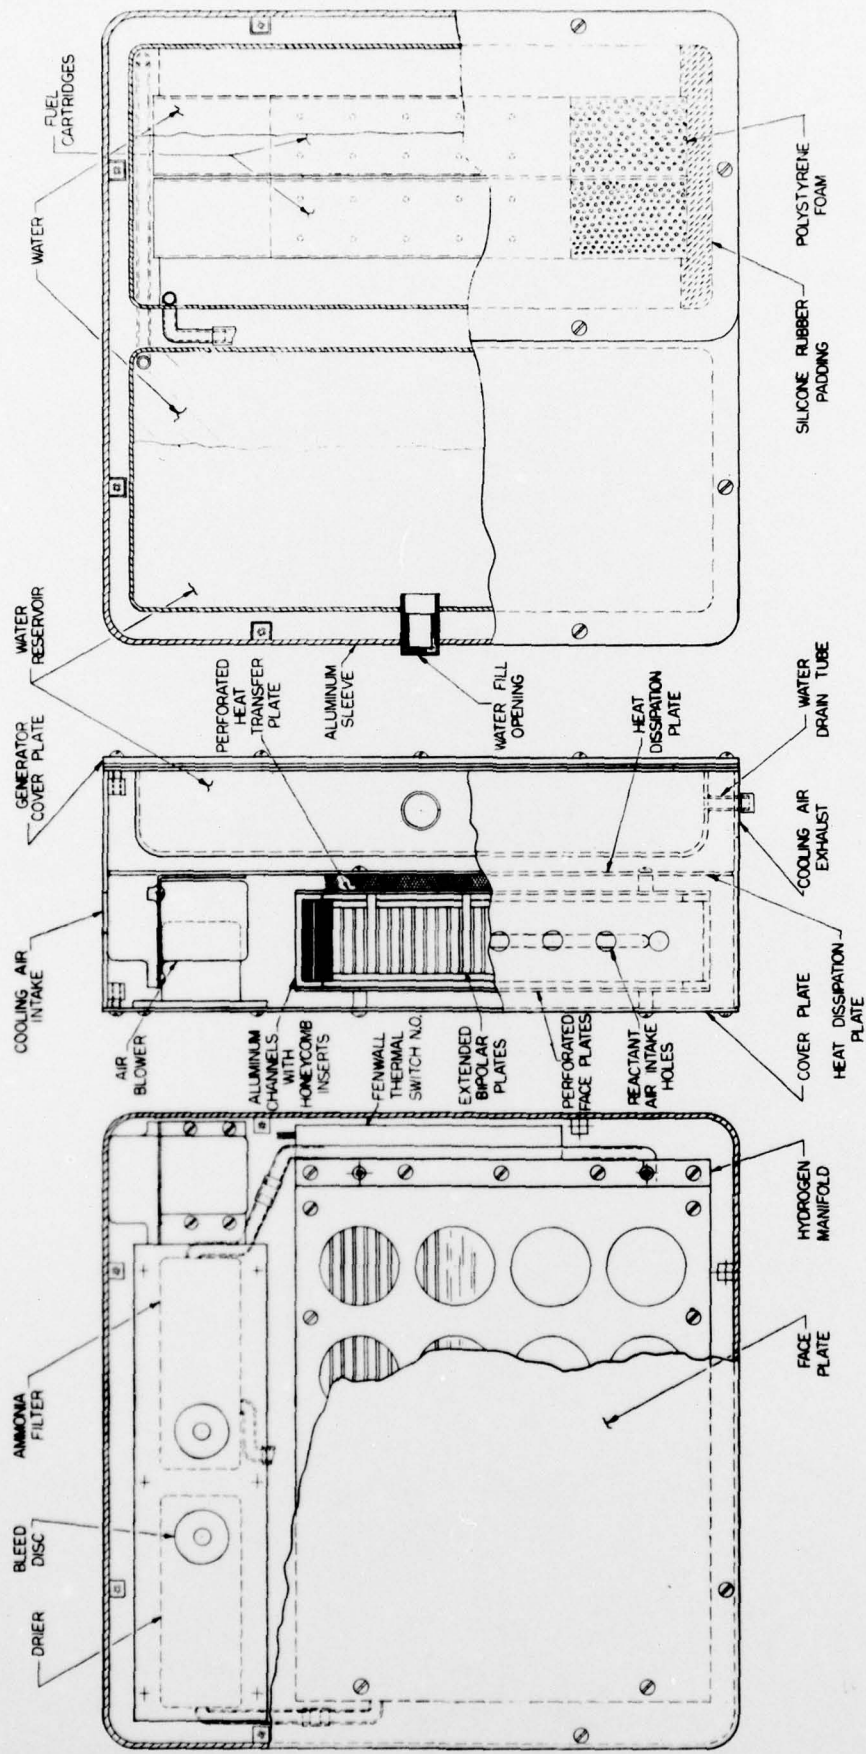

<b>INGERSOLL</b>	
FUEL CELL SYSTEMS	
TITLE 30 WATT SPE / HYDRIDE FUEL CELL SYSTEM	
DATE	NO. 10-30289
SCALE	

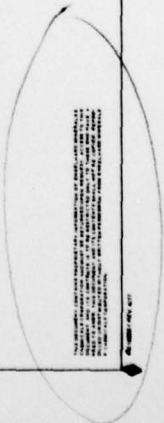

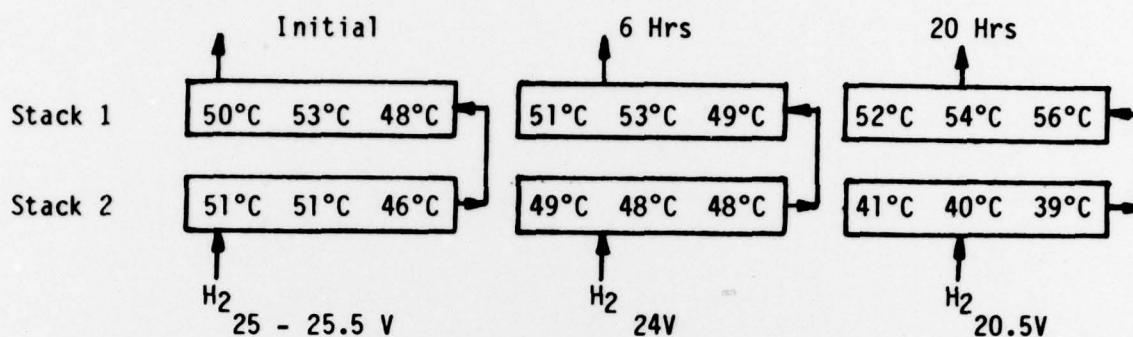

For uniform load sharing among parallel connected SPE stacks, thermal integration and limitation of the current supplied by each stack to a common load appears necessary.

Single Stack Design


Under phase 2, a single stack design with an active cell area of 48 cm<sup>2</sup> was developed. Temperature gradients in this design are small due to the high thermal conductivity of stack components. At rated load, variation over the entire stack are below 3°C. Gradients between the stack and the heat dissipating surface (Figure 2) range from 5-7°C. Most of the temperature drop takes place in the contact area between the bipolar plate and the face plate and is due to a coating applied to the bipolar plate for electrical insulation. Performance data representative for the four (4) stacks built under this program appear in Figure 6. At rated load, stack voltage varies by less than 1 volt. When the stacks are fully exposed to air, the output maximum is less than 30 watts. Changes in the design of the face plate and heat transfer structure may be required to improve oxygen transfer to the stack.

3.2.2 Hydrogen Generator Evaluation

The hydrogen generator meets or exceeds performance objectives outlined in Table 1. Start up is essentially instantaneous once water is added and hydrogen can be generated in excess of maximum load requirements up to a tilt angle of 45° from vertical. The hydride is utilized fully; however, in order to sustain a load of 30 watts and fully discharge the fuel, two cartridges have to be used simultaneously.

FIGURE 6 - CURRENT-VOLTAGE CHARACTERISTICS OF SPE POWER SOURCE

(See Table 2)

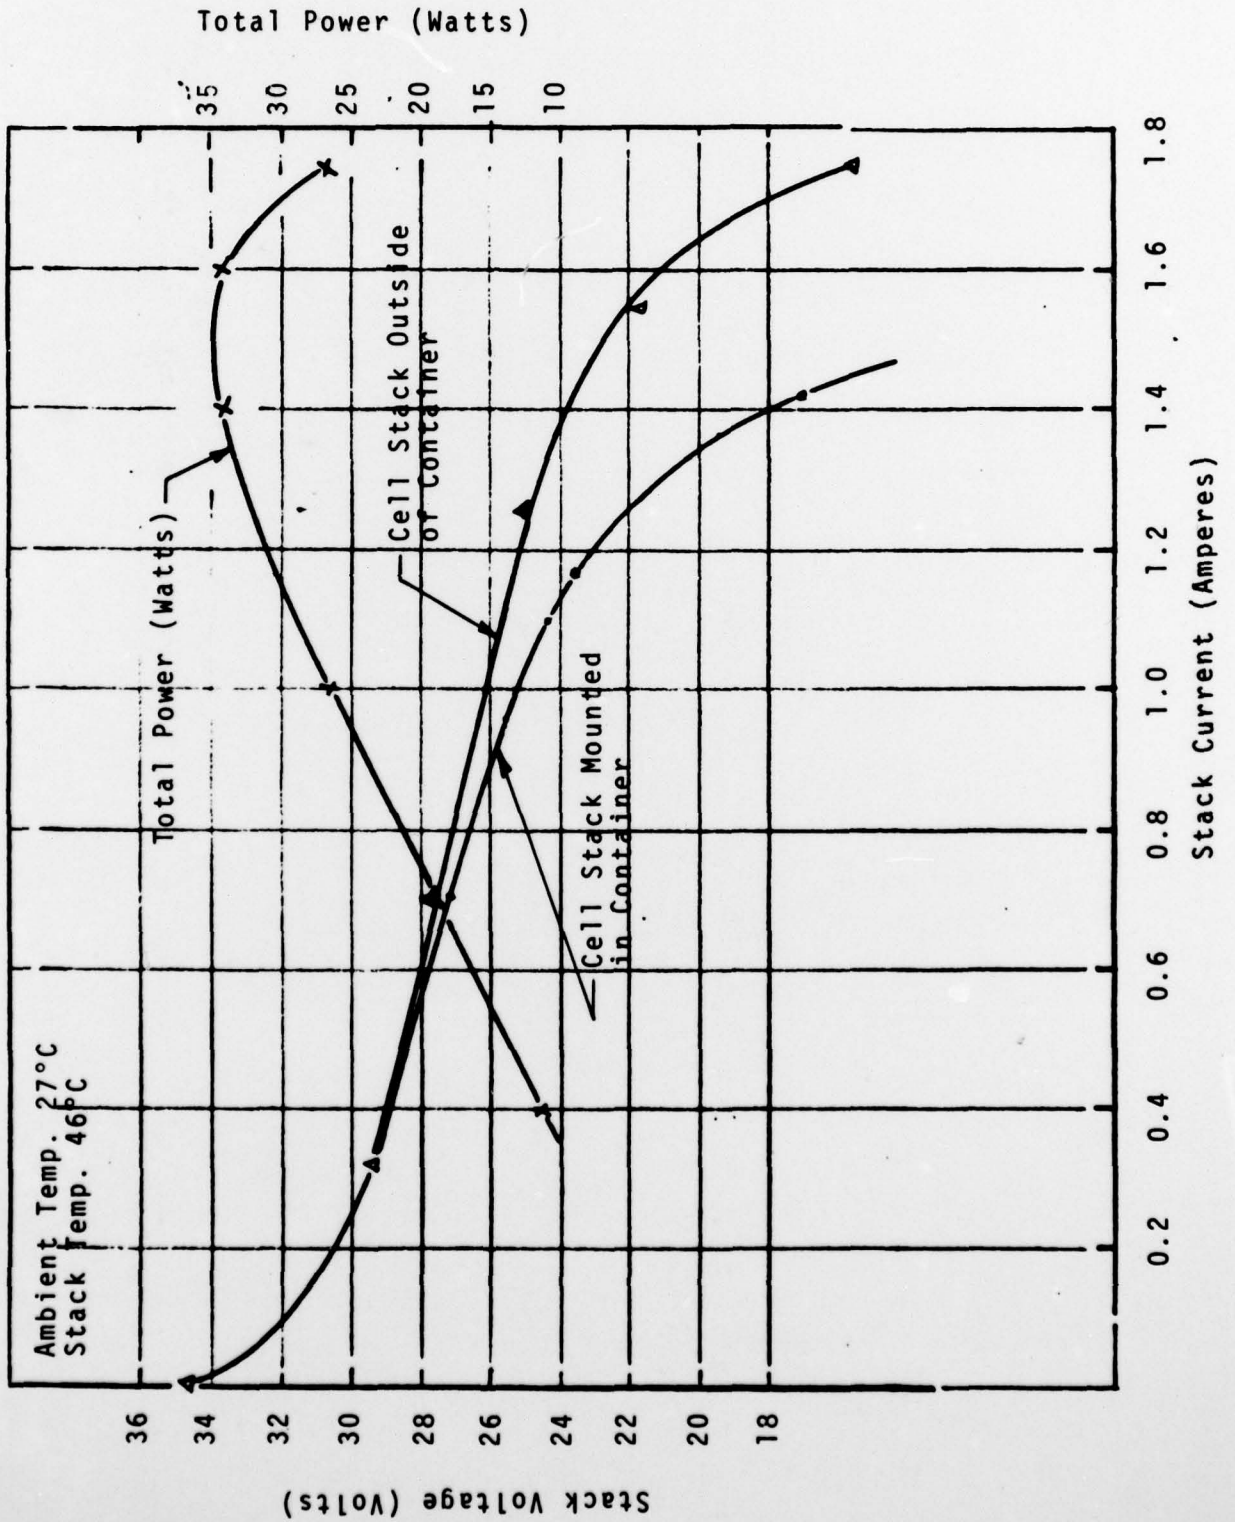

### Fuel Charge Per Cartridge

The optimum fuel charge per cartridge is 140 g. This value was determined in a series of experiments which are discussed below and summarized in Table 4. As indicated in Section 3.1.2, full utilization of the hydride and regulation of the hydrogen flow depend on the formation of a hydroxide cake of suitable porosity. It is obtained by providing room for expansion in the cartridge. This space is filled with polystyrene foam which, while gradually compressed during conversion, always keeps the fuel firmly packed, thus, preventing excessive water take up.

Location of the foam does not materially effect fuel utilization. Similar results were obtained whether the foam was inserted in intervals between portions of the fuel charge or simply used to plug the ends of the aluminum tube.

In one experiment the hydride was arranged in form of an annular ring and the center filled with foam. This arrangement may be of interest for cartridge configurations with larger diameter than used in this program.

Test data listed in Table 4 were obtained by discharging one cartridge only. It was placed 2.5 cm above the bottom of the reaction chamber. The hydrogen generated was metered directly or fed to the fuel which in these experiments was not thermally integrated with the generator. The results obtained from the discharge of one cartridge differ from the simultaneous discharge of two cartridges in the degree of water take up. Two cartridges take up proportionately more water because the cartridge located at the bottom of the reactor is discharged first, but continues to absorb water although hydrogen is supplied mostly from the second cartridge.

### Ammonia Content

Hydrogen generated from technical grade calcium hydride (Ventron Corp.) was found to contain approximately  $1.3 \times 10^{-3}$  val % ammonia corresponding to 0,25 mg per gram of calcium hydride converted.

For its removal, a scrubber cartridge containing Amberlyst 15, a sulfonic acid resin, was provided in the power source design. This arrangement proved unsatisfactory since under most conditions hydrogen is released from the generator not only water saturated but at a temperature well above that of the filter cartridge. Water condenses from the moist hydrogen causing plugging or by-passing of the resin bed.

Admixing the resin to the hydride directly does provide a suitable alternative and permits elimination of the filter cartridge. Thus, by adding 20 g Amberlyst 15 to a cartridge charge of 140 g -4 mesh calcium hydride, the amount of ammonia released was reduced to 0,05 mg/g from 0,25 mg/g. This may be further reduced by better dispersion of the absorbent which is utilized only to a very small degree.

**ENGELHARD**  
INDUSTRIES

FIGURE 7 - DISCHARGE CHARACTERISTIC OF HYDRIDE POWER SOURCE

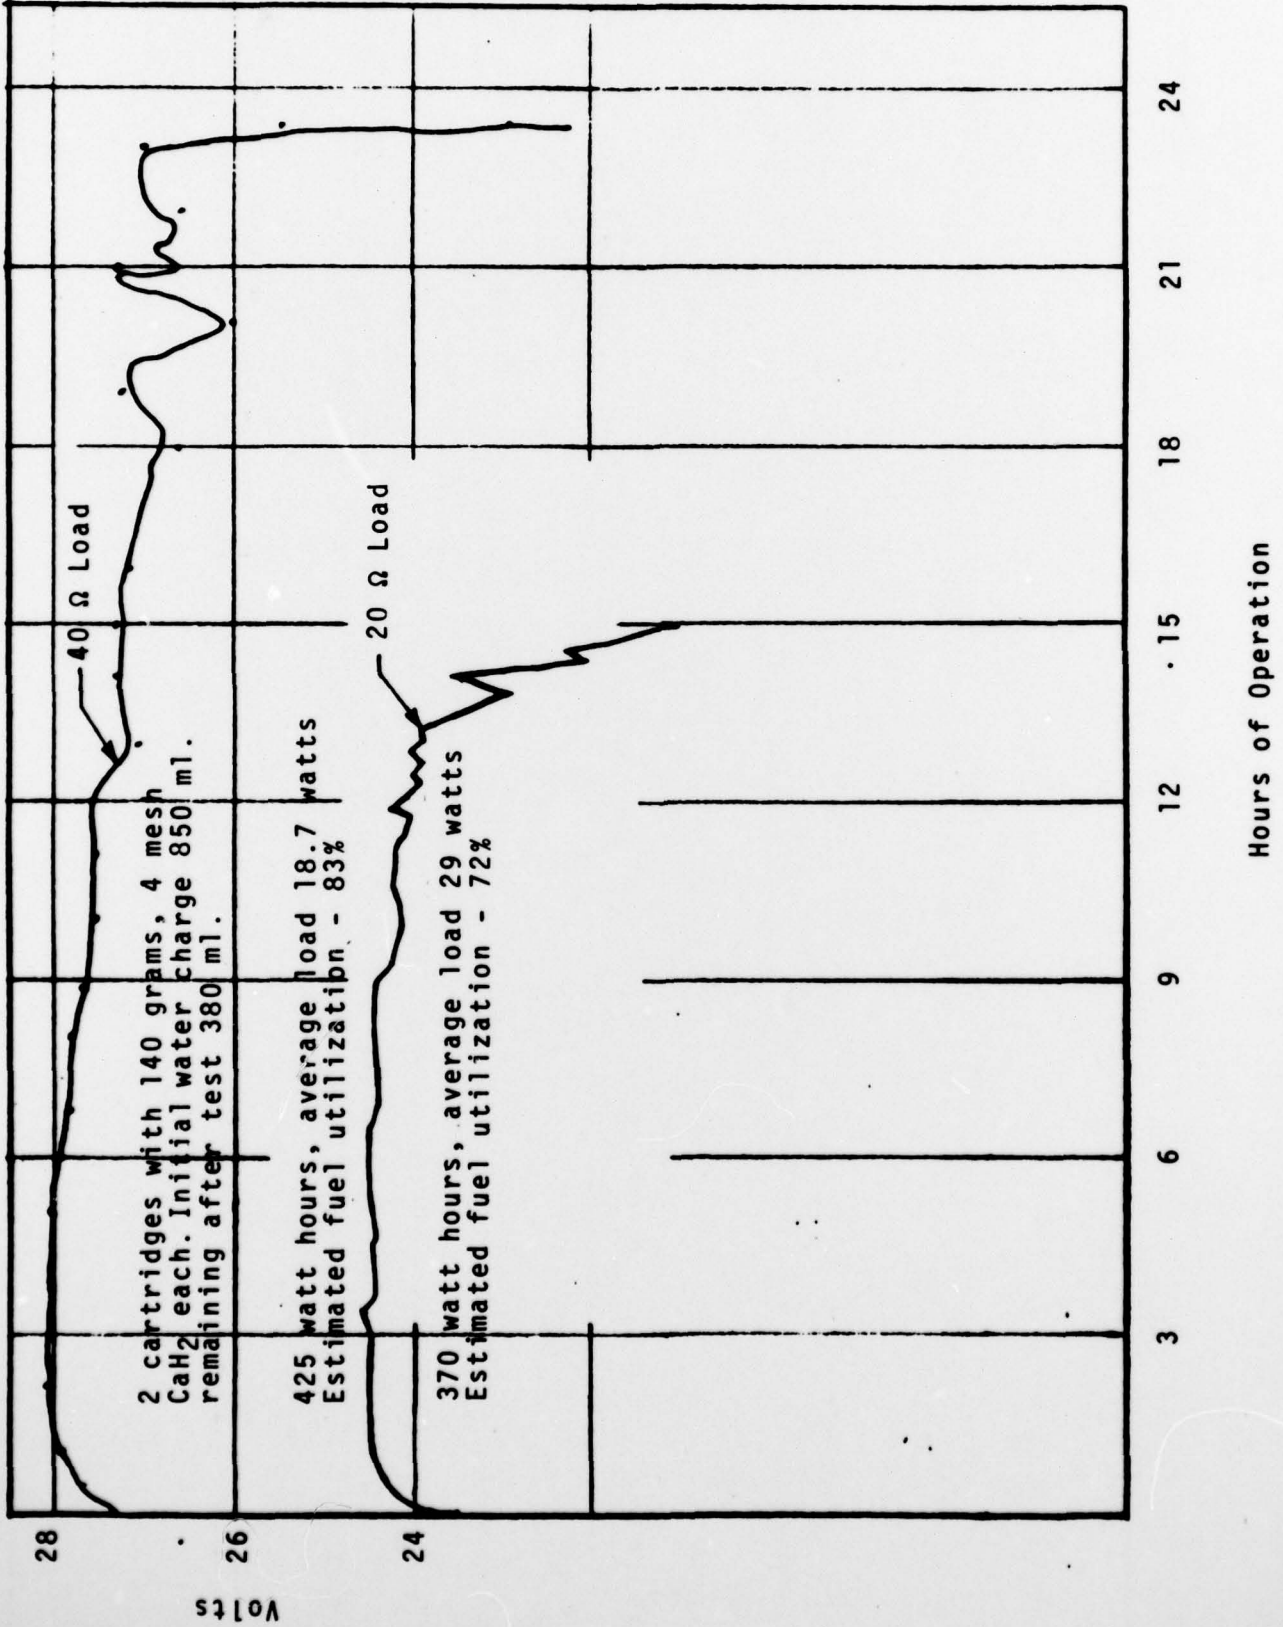


Table 4  
Hydride Utilization Experiments  
One Cartridge, Discharge with 40  $\Omega$  Load to 20 Volt Cutoff

Hydride Charge (g)	Watt Hrs to 20 Volt Cutoff	Water Consumed (ml)	Remarks
120	121	170	Fuel cell leak, polystyrene, foam plugs, fuel consumed.
130	173	--	Fuel consumed, polystyrene foam inserted in segments.
130	150	310	Poor regulation, 9 additional leaks, fuel consumed, hydroxide cake water soaked polystyrene foam plugs.
140	194	200	Fuel consumed, polystyrene foam plugs.
140	187	230	Annular arrangement of fuel foam in center, fuel used fully.
140	108	220	Fuel cell leak, fuel consumed, polystyrene foam plugs.
160	133	160	Significant amount of unconverted hydride, dense hydroxide cake.

### 3.2.3 Power Source Performance

Power source evaluation, including discharge experiments over periods of up to one day, was performed with only one of the two 30 watt hydride devices fabricated under the program.

In tests at room temperature, capacity requirements are exceeded by a factor of 3-4 and energy density requirements of 550 WH/kg for fuel acid water combined are met. Power output at 24 volts is below 30 watts due to the restricted air supply. If the fuel cell is removed from the container however, the required output level is reached.

Quick start-up is observed and power is delivered in less than one minute rather than fifteen minutes permissible. A higher purge rate is initially necessary at least with a new fuel cartridge. During start-up, fuel cell an generator are quickly purged but air trapped in a new fuel cartridge is only slowly released and does lead to inert gas build up at normal purge rates.

Figure 7 shows discharge characteristics of the integrated hydride system for a 20  $\Omega$  and 40  $\Omega$  load using two fuel cartridges. At the 20  $\Omega$  load level, additional air is supplied to the fuel cell. This test, therefore, does not reflect actual power source performance, however, it does indicate the capacity of generator and fuel cell to meet the required performance level. Discharge voltage varies within a range of 2 volts and some fluctuation was observed towards the completion of discharge due to erratic hydrogen generation.

#### 4.0 Conclusion and Recommendations

The development program carried out under contract DAAK 70-77-C-022 demonstrated the suitability of the SPE cell for the design of compact and reliable air breathing power sources. Its combination with a fuel such as calcium hydride provides -- even in short missions -- an energy to weight ratio far in excess of that available from conventional secondary batteries.

The system offers further convenience and speed of recharge by cartridge replacement.

Waste heat available from the fuel cell and the hydrogen generating reaction should permit operation at low temperatures without capacity loss. This possibility remains to be confirmed by additional testing.

Further development should focus on specific mission requirements and low temperature design.

DISTRIBUTION LIST

Commander (12)  
Defense Documentation Center  
Cameron Station, Bldg 5  
ATTN: TISIA  
Alexandria, VA 22314

Chief, Research, Development & Acquisition (1)  
Office, Deputy Chief of Staff  
Department of the Army  
Washington, DC 20310

Director (1)  
Technical Information  
Defense Advanced Research Projects Agency  
1400 Wilson Boulevard  
Arlington, VA 22209

Office of the Under Deputy Secretary (1)  
of Defense (Research & Advanced Technology)  
ATTN: ASST DIR, Electronics & Physical  
Sciences  
Washington, DC 20301

Commander (1)  
Headquarters, US Army Material Development  
& Readiness Command  
ATTN: DRCDE-D  
5001 Eisenhower Avenue  
Alexandria, VA 22304

Commander (1)  
US Army Electronics R&D Command  
ATTN: DRSEL-KL-P  
Fort Monmouth, NJ 07703

Commander (1)  
US Army Transportation Research & Engineering  
Command  
ATTN: Research Directorate  
Fort Eustis, VA 23604

Commander (1)  
Harry Diamond Laboratories  
DELHD-RDD (Benderly)  
Adelphi, MD 20783

Chief, (1)  
US Army Security Agency  
Arlington Hall Station  
Arlington, VA 22212

DOD Project Manager-Mobile Electric  
Power (1)  
ATTN: DRCPM-MEP-TM  
7500 Backlick Road  
Springfield, VA 22150

Technical Documents Center (2)  
US Army Mobility Equipment R&D Command  
ATTN: DRDME-WC  
Fort Belvoir, VA 22060

Commander (1)  
US Army Tank-Automotive R&D Command  
Technical Library/DRDTA-UL  
Warren, MI 48090

Chief (1)  
Naval Ships Engineering Center  
Department of the Navy  
ATTN: Code 6157D, Mr. Albert Himy  
Washington, DC 20362

Director, Power Branch (1)  
Office of Naval Research  
ATTN: 473,  
800 N. Quincy Street  
Arlington, VA 22217

Department of the Navy (1)  
Office of Naval Research  
Ballston Tower #1  
Code: 472, Room 624  
800 N. Quincy Street  
Arlington, VA 22217

Commander (1)  
Naval Ordnance Test Station  
China Lake, CA 93555

Commander (1)  
US Naval Electronics Laboratory  
ATTN: Research Library  
San Diego, CA 92152

Director (1)  
US Naval Research Laboratory  
ATTN: Code 2027  
Washington, DC 20390

DISTRIBUTION LIST

Office of Naval Research (1)  
Department of the Navy  
ATIN: Code 425  
800 N. Quincy Street  
Arlington, VA 22217

Commanding Officer (1)  
Naval Ships R&D Center  
Annapolis Division  
Annapolis, MD 21402

Power Information Center (1)  
University City Science Center  
3624 Science Center  
Philadelphia, PA 19104

Commanding Officer (10)  
US Army Mobility Equipment R&D Command  
Electrical Power Laboratory  
ATIN: DRDME-EC (Systems Group)  
Fort Belvoir, VA 22060

Commander (1)  
US Air Force Security Service  
ATIN: DCS/Communications-  
Electronics (ESO)  
San Antonio, TX 78241

Commander (1)  
Aerospace Power Division  
ATIN: AFAPL/PO (Mr. J.D. Reams)  
Wright-Patterson Air Force Base  
Dayton, OH 45443

Commander (1)  
Department of the Air Force (AFSC)  
Rome Air Development Center  
ATIN: TUGG (Mr. F.J. Mollura, 3068)  
Griffiss, AFB, NY 13441

Commander (1)  
AFEWC (SURP)  
San Antonio, TX 78241

Commander (1)  
Marine Coprs Development & Education  
Center  
ATIN: M&L Division (M. Horstkamp)  
Quantico, VA 22134

Mr. Norman Rosenberg (1)  
US Department of Transportation  
Transportation Systems Center  
55 Broadway  
Cambridge, MA 02142

US Department of Energy (1)  
ATIN: Mr. Gary Voelker  
20 Massachusetts Avenue, NW  
Washington, DC 20545

Dr. Paul C. Milner (1)  
Bell Telephone Laboratories  
Murray Hill, NJ 07974

Electrochimica Corporation (1)  
2485 Charleston Road  
ATIN: Mr. V. Sparks, Technical Library  
Mountain View, CA 94040

Engelhard Minerals & Chemical Corp (1)  
Engelhard Industries Division  
Government Services Department  
ATIN: Mr. V.A. Forlenza  
70 Wood Avenue, South  
Metro Park Plaza  
Iselin, NJ 08830

Exxon Research & Engineering Company (1)  
PO Box 8  
ATIN: Dr. G. Ciprios  
Linden, NJ 07036

General Electric Company (1)  
50 Fordham Road  
ATIN: L.J. Nuttall, Bldg 1A  
Wilmington, MA 01887

Institute of Gas Technology (1)  
3434 South State Street  
ATIN: Dr. K.F. Blurton  
Chicago, IL 60616

Electric Power Research Institute (1)  
ATIN: A.P. Fickett  
PO Box 10412  
Palo Alto, CA 94304

Globe-Union Inc (1)  
ATIN: Corporate Research  
5757 North Green Bay Avenue  
Milwaukee, WI 53201

DISTRIBUTION LIST

Director (1)  
George Marshall Space Flight Center  
ATIN: M-ASTR-E  
Huntsville, AL 38809

Director (1)  
Lewis Research Center  
National Aeronautics & Space Administration  
ATIN: Mr. H.J. Schwartz (M.S. 309-1)  
21000 Brookpark Road  
Cleveland, OH 44135

Argonne National Laboratory (1)  
9700 South Cass Avenue  
ATIN: Dr. Paul Nelson, Bldg. 205  
Argonne, IL 60439

Commanding Officer (1)  
US Army Signal Warfare Laboratory  
ATIN: DELSW-CC, Mr. Crabbe  
Arlington Hall Station, VA 22212

Government of Canada (1)  
ATIN: Mr. C.L. Gardner  
2122 Rushton Road  
Ottawa, Ontario, Canada KZ1N7

Gas Research Institute (1)  
ATIN: Dr. Lloyd R. Lawrence, Jr.  
3424 South State Street  
Chicago, ILL 60616

Dr. Ralph Roberts (1)  
Energy Resources & Environmental Systems  
Engineering  
The MITRE Corporation  
Mail Stop W-389  
Westgate Research Park  
McLean, VA 22101

Universal Oil Products, Inc. (1)  
Ten UOP Plaza  
ATIN: Stephen N. Massie  
Government Contract Administrator  
Des Plaines, IL 60016

Technology Center (1)  
ESB Incorporated  
19 W. College Avenue  
ATIN: Dr. D.T. Ferrell, Jr.  
Yardley, PA 19067

Power Systems Division (1)  
United Technologies Corporation  
ATIN: Mr. Al Meyer  
PO Box 109, Governor's Highway  
South Windsor, CT 06074

Union Carbide Corporation (1)  
Parma Research Center  
PO Box 6166  
ATIN: Dr. R. Brodd  
Parma, OH 44101

Dr. S.B. Brummer (1)  
Director of Physical Research  
EIC, Inc.  
55 Chapel Street  
Newton, MA 02158

Shell Development Company (1)  
ATIN: Dr. D.C. Olson  
PO Box 262  
Wood River, ILL 62095

IIT Research Institute (1)  
ATIN: Mr. Edward Fochtman  
10 West 35th Street  
Chicago, IL 60616

Dr. P. Stonehart (1)  
Stonehart Associates, Inc.  
34 Five Fields Road  
Madison, CT 06443

Jet Propulsion Laboratory (1)  
California Institute of Technology  
ATIN: Dr. John Houseman, Supervisor  
Fuel Conversion Group  
4800 Oak Drive  
Pasadena, CA 91103

Massachusetts Institute of Technology (1)  
ATIN: Professor H.P. Meissner  
Cambridge, MA 02138

U.C.L.A. (1)  
Department of Chemical Engineering  
ATIN: Prof. D. Bennion  
Los Angeles, CA 90007

Institute of Defense Analysis (1)  
400 Army-Navy Drive  
Arlington, VA 22202

DISTRIBUTION LIST

Director (1)  
National Aeronautics & Space Administration  
ATTN: Code RPP, Mr. A. Dan Schnyer  
Washington, DC 20546

Energy Research Corporation (1)  
ATTN: Dr. B. Baker  
3 Great Pasture Road  
Danbury, CT 06810

University of Wisconsin (1)  
Department of Chemical Engineering  
ATTN: Professor S. H. Langer  
Madison, WI 53706