

AD-A072 716


NAVAL AVIONICS CENTER INDIANAPOLIS IN  
DELETERIOUS EFFECT OF FUSING FLUIDS ON PRINTED WIRING BOARDS.(U)  
MAY 79 D O POND  
NAC-TR-2259

F/G 9/5


UNCLASSIFIED

NL

| OF |  
ADA  
072716

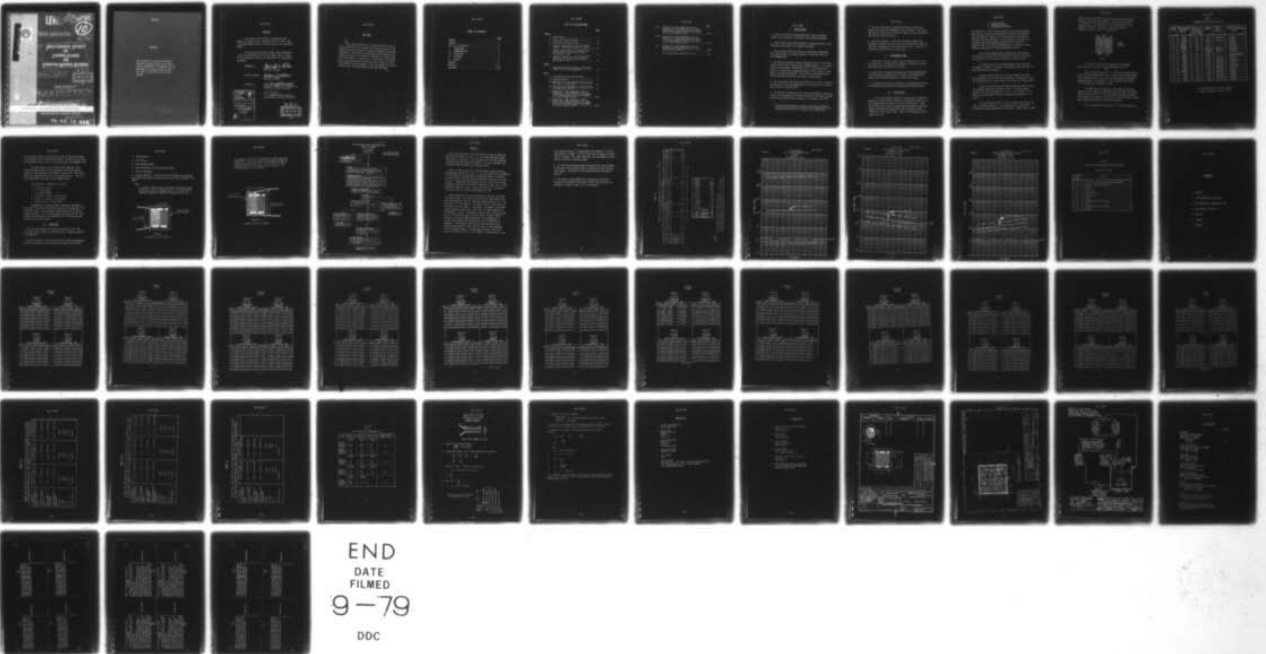

END  
DATE  
FILMED  
9-79  
DDC



MICROCOPY RESOLUTION TEST CHART

NATIONAL BUREAU OF STANDARDS-1963-A



NAC-2259

NOTICE

The discussions or opinions concerning commercial products herein do not constitute an endorsement or condemnation by the Government, nor do they convey or imply the right to a license for use of such products.

NAC TR-2259

## PREFACE

This report covers the work performed by NAC's Materials Laboratory from 1 December 1978 to 30 April 1979 on the deleterious effect of fusing fluids on printed wiring boards.

This work was performed for RADC, under sponsorship of Mr. John McCormick, Rome Air Development Center's Reliability Laboratory, Griffiss Air Force Base, NY; FQ761070032 BCN 90474.

PREPARED BY:

David O. Pond  
DAVID O. POND  
Materials Engineer

PROJECT ENGINEER:

William T. Hobson  
WILLIAM T. HOBSON  
Materials Engineer

APPROVED BY:

Michael G. Cowart  
MICHAEL G. COWART, Head, Consultants  
and Materials Services Branch

B. P. Vaughn  
B. C. VAUGHN, Director, Materials  
Laboratory and Consultants Division

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced Justification	<input type="checkbox"/>
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or special
A	

DDC  
RECEIVED  
AUG 14 1979  
D



TABLE OF CONTENTS

	<u>PAGE</u>
PREFACE . . . . .	i
ABSTRACT . . . . .	ii
LIST OF ILLUSTRATIONS . . . . .	iv
I. CONCLUSIONS . . . . .	1
II. RECOMMENDATIONS . . . . .	2
III. DISCUSSION . . . . .	2
IV. PROCEDURE . . . . .	8
V. RESULTS . . . . .	12
APPENDIX . . . . .	A-1
MATERIALS . . . . .	A-24
EQUIPMENT . . . . .	A-25

LIST OF ILLUSTRATIONS

	<u>PAGE</u>
<b>FIGURES</b>	
1. Comb Pattern .....	4
2. Solder Mask Coated Specimen .....	9
3. Conformally Coated Specimen .....	10
4. Graph, 72 Hour Delay (A, B and C Fusing Fluids) - Controls-Resistance vs Time.....	15
5. Graph, 72 Hour Delay - "A" Fusing Fluid, 0 Volts Stress, Conformally Coated - Resistance vs Time .....	16
6. Graph, 72 Hour Delay - "A" Fusing Fluid, 100 Volts Stress, Conformally Coated - Resistance vs Time .....	17
<b>CHARTS</b>	
1. Flow Chart for Water-Soluble and Non-Water Soluble Fusing Fluid Specimens.....	11
<b>TABLES</b>	
I. Characterization of Fusing Fluids .....	5
II. Experiment Matrix .....	6
III. Humidity & Elevated Temperature Resistances Less Than $1.5 \times 10^8$ ohms .....	14
IV. Infra-red Spectrophotometer Characterization of Fusing Fluids Tested.....	18
V. Formula for Linear Regression Lines of Resistance vs Time and Analysis of Slopes - 72 Hour Delay Before Fusing Fluid Removal - (A, B and C Fusing Fluids) .....	A-16
VI. Formula for Linear Regression Lines of Resistance vs Time and Analysis of Slopes - 168 Hour Delay Before Fusing Fluid Removal - (A, B and C Fusing Fluids) .....	A-17

NAC TR-2259

	<u>PAGE</u>
VII. Formula for Linear Regression Lines of Resistance vs Time and Analysis of Slopes - 168 Hour Delay Before Fusing Fluid Removal - (A, B, and C Fusing Fluids) .....	A-18
VIII. Formula for Linear Regression Lines of Resistance vs Time and Analysis of Slopes - 72 Hour Delay Before Fusing Fluid Removal - (J, L, and O Fusing Fluids) .....	A-19
IX. Formula for Linear Regression Lines of Resistance vs Time and Analysis of Slopes - (M and N Fusing Fluids) .....	A-20
X. MIL-P-28809 Ionic Contaminants Test .....	A-21

## I. CONCLUSIONS

1. Seven of the fusing fluids tested had a minimal degrading effect on the insulation resistance of the prepared specimens.
2. Four of the fusing fluids tested had a degrading effect on the insulation resistance of the prepared specimens.
3. The insulation resistance testing of specimens contaminated with fusing fluids is a better measure of cleanliness than the MIL-P-28809 method.
4. The infra-red spectrophotometer characterization of the fusing fluids indicates that seven of them contained glycols. In a report<sup>1</sup> given at the September 1978 meeting of IPC, it was stated that glycols in fluxes have a degrading effect on the insulation resistance of printed-wiring boards. The results of this study do not confirm this when the glycols are used in fusing fluids.
5. The test results from the fusing fluids do not provide sufficient statistical data for the preparation of a first draft of a military specification on fusing fluids.
6. The analysis of variance (anova) testing performed on resistance values of the contaminated specimens indicated the difference between the 0 VDC and 100 VDC stress specimens is not always significant.

<sup>1</sup> *"Printed-Wiring Assembly Insulation Resistance Degradation Caused by Nonionizing Water-Soluble Flux Residues", Dr. Frank Zado, Western Electric Co., Princeton, NJ (UNPUBLISHED)*

7. The anova indicated a significant difference between the solder mask coated and conformally coated specimens. The solder mask material gave greater protection against moisture penetration than did the conformal coating.

8. The anova revealed a significant difference between the measured resistances for the 72 hour and 168 hour delay times for specimens contaminated with fusing fluids A and B. There was no significant difference with fusing fluid C.

## II. RECOMMENDATIONS

1. Insulation resistance testing should be performed by a user of fusing fluids to determine the deleterious effect on printed-wiring boards of the fluids he is using.
2. Insulation resistance testing and not the MIL-P-28809 method should be used to determine the cleanliness of printed-wiring boards which have been subjected to fusing fluid usage.
3. Insulation resistance testing should be performed on printed-wiring boards which have been contaminated with known glycols.

## III. DISCUSSION

In the electronics industry, a fusing fluid is generally defined as a heat-transfer liquid for fusing applications such as the reflow melting of solder on printed wiring boards. Since fusing fluids do not have to promote the wetting of a metal with solder, they would not necessarily have to contain the same chemicals as rosin based fluxes. Some of the chemicals in rosin based fluxes are:

1. Wetting agents
2. Oxidation removers
3. Reoxidation preventers

The question as to the corrosive effect of rosin based activated (RA) fluxes on printed wiring boards has already been addressed. Since the chemical composition of fusing fluids is not known by the user, the question arose: is the insulation resistance of a printed wiring board degraded by fusing fluids as they are presently used in electronics manufacturing? At present, fusing fluids are not under a military specification control.

Rome Air Development Center requested that NAC evaluate the effects of fusing fluids on printed wiring boards and prepare a first draft for a military specification on fusing fluids.

A literature survey was conducted before this experiment was started. However, it yielded no information about the type of experiment that was performed.

Sixteen fusing fluids were chosen at random from fusing fluid manufacturers for use in this experiment. Eleven were tested. The characterization of the sixteen fusing fluids is shown in Table I.

Eight of the eleven fusing fluids tested were water soluble. The remaining three were insoluble in water. The eight water soluble fluids were designated "A, B, C, J, L, M, N, and O". The three fluids which were insoluble in water were designated "F, I, and K".

The comb pattern shown in Figure 1 (page 4) was used as the basic resistance specimen. It was produced using conventional printed wiring board manufacturing techniques. Historically, a comb

pattern specimen has been associated with printed wiring board insulation resistance measurements. This particular pattern is a duplicate of the one used in the IPC Round Robin on the "Additive Process for Producing Printed Wiring Boards". (Dimensions on Dwg. AV22107 in the Appendix.)



Figure 1.

A total of 325 comb pattern specimens was produced. Approximately 48 specimens were used for each test run.

Using resistance squares,  $1.5 \times 10^8$  ohms insulation resistance on the comb pattern was found to be equivalent to 500 megohms on the trumpet pattern in MIL-P-55110C (equilibration calculation shown on page A-22 in the Appendix). Any resistance value below  $1.5 \times 10^8$  ohms was considered a failure.

The experiment was designed so that some test specimens within a test set were very clean when they were ready for temperature and humidity stress. These specimens were used to determine if the copper clad laminate from which all the comb pattern specimens were produced contained any electrical anomalies.

The "Experiment Matrix", Table II, is a visual description

TABLE I.

## CHARACTERIZATION OF FUSING FLUIDS

FUSING FLUID	*WATER EXTRACT RESISTIVITY OHM-CM	pH(0.1 ml of FLUID DILUTED W/ 50 ml H <sub>2</sub> O)	% RESIDUE AT 500°F	CHLORIDE ION INDICATION	WATER SOLUBILITY 1 PART FLUID/4 PARTS H <sub>2</sub> O
A	5600	4.1	7.52	Positive	Soluble
B	14300	4.4	0.69	Positive	Soluble
C	901300	5.6	3.92	?	Soluble
D	907000	4.8	3.84	?	Emulsion
E	156000	4.6	44.11	Negative	Insoluble
F	74670	**	64.53 @ 100°C	Negative	Insoluble
G	10150	4.2	10.79	?	Cloudy Solution
H	6650	3.7	6.08	Positive	Soluble
I	73300	5.9	68.50	Negative	Insoluble
J	6020	4.1	1.77	Positive	Soluble
K	71700	5.1	79.64	Negative	Insoluble
L	5300	4.1	1.69	Positive	Soluble
M	360000	5.5	3.24	Negative	Soluble
N	6750	4.1	6.20	Positive	Soluble
O	2950	3.6	3.22	Positive	Soluble
P	8270	4.0	3.37	Positive	Soluble

\* Performed according to MIL-F-14256D

\*\* Unable to obtain, insoluble in H<sub>2</sub>O

TABLE II.  
EXPERIMENT MATRIX  
RESISTANCE READINGS DURING HUMIDITY & ELEVATED TEMPERATURE STRESSING  
MIL-STD-810C, METHOD 507.1, PROCEDURE I.

SPECIMENS PER SET	A <sup>1</sup> 0 <sup>2</sup> C <sup>3</sup> A100C A0S A100S			R < 1.5x10 <sup>8</sup> Ω DURING TESTING			B0C B100C B0C B100S			R < 1.5x10 <sup>8</sup> Ω DURING TESTING			C0C C100C C0S C100S			R < 1.5x10 <sup>8</sup> Ω DURING TESTING			
	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4	4	
DAYS	72 HOUR DELAY BEFORE FUSING FLUID REMOVAL																		
1																			
2																			
3																			
4																			
5																			
6																			
7																			
8																			
9																			
10																			
DAYS	168 HOUR DELAY BEFORE FUSING FLUID REMOVAL																		
1																			
2																			
3																			
4																			
5																			
6																			
7																			
8																			
9																			
10																			

1 First letter indicates fusing fluid used.  
2 Number will either be 0(no DC voltage) or 100(DC volts).  
3 Last letter indicates conformal coated(C) or solder mask(S).

NAC TR-2259

of how the experiment was designed. Those specimens within a test set were divided into lots which were then contaminated with the fusing fluids. Some test specimens within a fusing fluid lot were stressed with 100 volts DC, while other test specimens were not voltage stressed. Some test specimens within a fusing fluid lot were solder mask coated, while others were conformally coated. The test specimens which were tested for electrical anomalies were neither voltage stressed nor coated. Within each fusing fluid lot there were enough specimens provided to permit the data obtained to be analyzed statistically.

The fusing fluids were tested in groups of three for each test run. There was a total of 48 specimens for each group of three. This gave a possibility of five control specimens, since the maximum which would be loaded into the humidity chamber was 53 specimens.

The MIL-P-28809 Ionic Contaminants Test was used on a sampling basis to monitor boards from the same process lot for cleanliness. (These sampled boards were not temperature and humidity stressed.)

Time between fusing fluid fusing and cleaning was the variable chosen to differentiate between temperature and humidity stress runs for fusing fluids A, B, and C. The two delay times between fusing fluid fusing and cleaning were chosen to simulate fabrication cycles with 1) 72 hours standing over a weekend, or 2) 168 hours for boards touched up or otherwise held in process for one week. The remaining fusing fluids were subjected to a 72 hour delay time only.

The temperature and humidity conditions of MIL-STD-810C Environmental Test Methods, Method 507.1, Procedure I, were used.

This was done because fusing fluids are used to fabricate printed wiring boards used in electronic equipment. Ultimately the printed wiring boards survive or fail in the environment the equipment sees.

The resistances of the specimens were measured in the humidity chamber during the high temperature and high humidity portion of the temperature and humidity stress cycle. The resistances were measured on 24 hour cycles on working days. The resistance measurements were made using a megohm bridge.

The experiment proceeded in this order:

1. Fluids A, B, and C
  - A. 72 hour delay
  - B. 168 hour delay
2. Fluids F, I, and K - 72 hour delay
3. Fluids J, L, and O - 72 hour delay
4. Fluids M and N - 72 hour delay

An analysis of variance (anova) testing was performed to form conclusions about data collected during this experiment. The resistance values of the specimens contaminated with the fusing fluids were used. The resistance values used were from the third, seventh, and tenth days of measurement after initiating the test for each fusing fluid tested.

#### IV. PROCEDURE

1. Make 325 comb pattern printed wiring boards of FL-GF, .062 C 1/1 glass epoxy laminate to conform to Dwg. AV 22109 on page A-27 in the Appendix.
2. Mask the laminate, using dry film resist so that the conductor pattern and the back of the printed wiring board can be plated.

3. Tin/lead plate.
4. Strip resist.
5. Etch unplated copper.
6. Rinse thoroughly in tap water and blow dry.
7. Rout out specimens.
8. Prepare specimens. The flow chart and procedure for producing the water soluble and non-water soluble fusing fluid specimens is on page 11.

*NOTE:*

*A. Figure 2 shows how the solder mask coated specimen was constructed. Solder mask was applied to the comb specimen which was governed by conductor pads 1, 2, and ½ of 3. Electrical leads were soldered to conductor pads 1 and 2.*

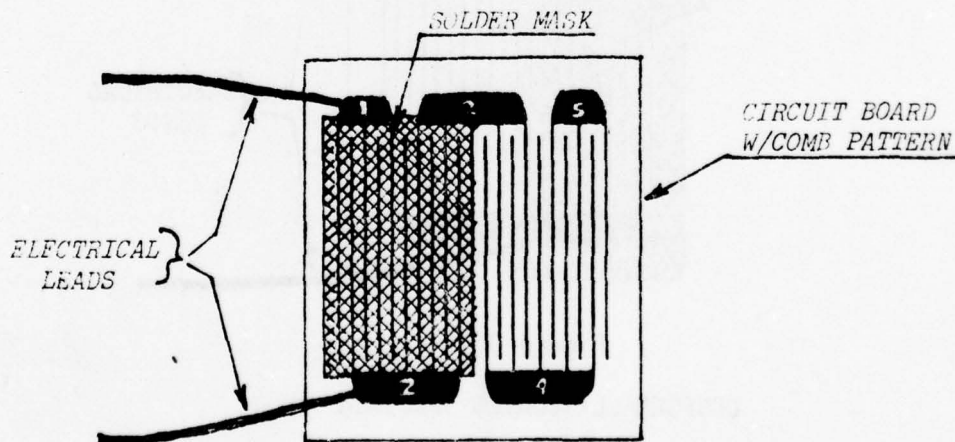


Figure 2.

SOLDER MASK COATED SPECIMEN

B. Figure 3 shows how the conformally coated specimen was constructed. Electrical leads were soldered to conductor pads 1 and 2. The leads exited the specimen from the end opposite conductor pads 1 and 2. This allowed the comb specimen governed by conductor pads 1, 2 and  $\frac{1}{2}$  of 3 to be conformally coated by dipping.


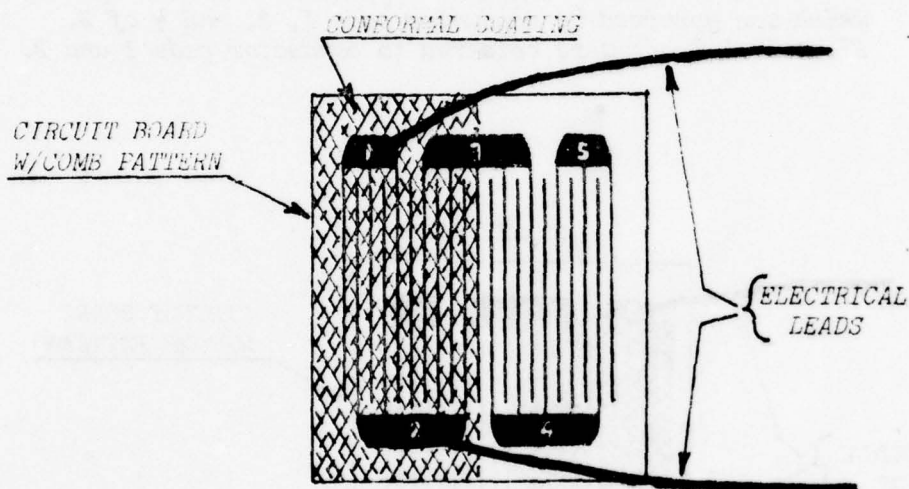


Figure 3.  
CONFORMALLY COATED SPECIMEN

FLOW CHART FOR WATER SOLUBLE AND NON-WATER SOLUBLE  
FUSING FLUID SPECIMENS

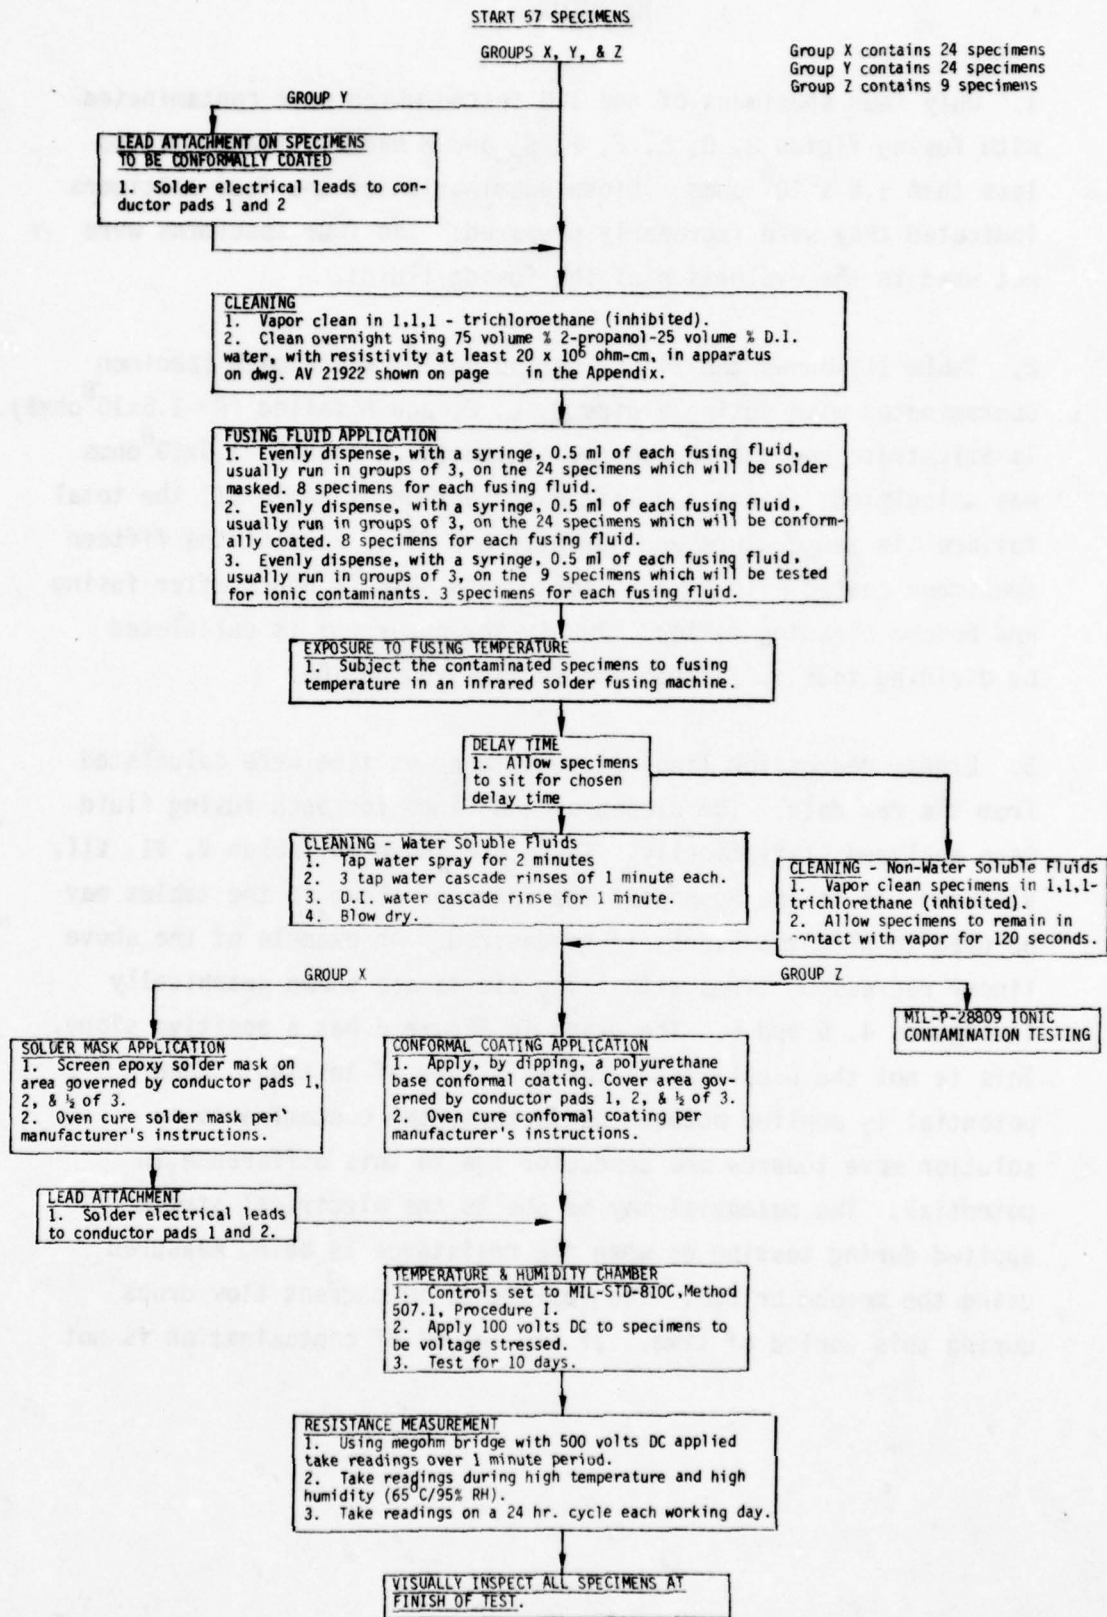

## RESULTS

1. Only four specimens of the 160 tested which were contaminated with fusing fluids A, B, C, F, I, K, and M had resistance values less than  $1.5 \times 10^8$  ohms. Close examination of the four specimens indicated they were improperly prepared. The four specimens were not used in the evaluation of the fusing fluids.
  
2. Table III shows the 24 hr. period during which each specimen contaminated with fusing fluids J, L, O, and N failed ( $R < 1.5 \times 10^8$  ohms). To illustrate how the percentage of specimens with  $R < 1.5 \times 10^8$  ohms was calculated, in the top left hand section of Table III the total failure in temperature and humidity was 27%. Four of the fifteen specimens coated with fusing fluid J and held 72 hours after fusing and before cleaning failed. Twenty-seven percent is calculated by dividing four by fifteen and multiplying by 100.
  
3. Linear regression lines of resistance vs time were calculated from the raw data. The slopes of the lines for each fusing fluid were analyzed statistically. These are shown on Tables V, VI, VII, VIII and IX in the Appendix. The formulas shown in the tables may be used to plot the lines, if so desired. An example of the above linear regression lines with  $\pm 3\sigma_y$  limits are shown graphically in Figures 4, 5 and 6. The graph in Figure 6 has a positive slope. This is not the usual result for this type of testing. When a potential is applied between conductors, the contaminants in solution move towards one conductor due to this difference in potential. The potential may be due to the electrical stress applied during testing or when the resistance is being measured using the megohm bridge. The resistance to current flow drops during this period of time. If the amount of contamination is not

great enough to cause a "bridge" between the conductors, a resistance barrier is formed. This will cause the resistance to current flow to increase. The linear regression line calculated can then result in one with a positive slope.

4. An infra-red spectrophotometer characterization was performed on the eleven fusing fluids tested to identify the main constituents therein. The results of the characterization are shown in Table IV.

5. The values on MIL-P-28809 ionic contamination testing of fusing fluid contaminated specimens retained from each test run are shown in Table X., page A-21 in the Appendix.

TABLE III.

HUMIDITY & ELEVATED TEMPERATURE RESISTANCES LESS THAN  $1.5 \times 10^8$  OHMS

MIL-STD-810C, METHOD 507.1, PROCEDURE 1.

DATE (1979)	DAY	P is less than $1.5 \times 10^8$ Ohms		L-0C L100C L0S L100S		R is less than $1.5 \times 10^8$ Ohms		Totals	R is less than $1.5 \times 10^8$ Ohms	
		J100C J0S J100S	Totals	L-0C L100C L0S L100S	Totals	O0C O100C O0S O100S	Totals			
*3 72 Hour Delay Before Fusing Fluid Removal										
2 Apr	3									
3 Apr	4	4								
4 Apr	5									
5 Apr	6									
6 Apr	7									
9 Apr	10									
TOTALS		4	0	0	0	4	27%	4	25%	3 1 0 0 4 25%

\* ( ) Indicates number of specimens, 4 specimens were normally used.

DATE (1979)	DAY	P is less than $1.5 \times 10^8$ Ohms		M100C M0S M100S		Totals	R is less than $1.5 \times 10^8$ Ohms
		N100C N0S N100S	Totals	M100C M0S M100S	Totals		
72 Hour Delay Before Fusing Fluid Removal							
23 Apr	3						
24 Apr	4	4					
25 Apr	5						
26 Apr	6						
27 Apr	7						
30 Apr	10						
TOTALS		4	2	0	0	6	38%

- LEGEND:
- 1 First letter indicated fusing fluid used.
  - 2 Number will either be 0 (no DC voltage) or 100 (DC volts).
  - 3 Last letter indicates conformal coated (C) or solder mask (S).

FIGURE 4. 72 HOUR DELAY  
(A, B, AND C FUSING FLUIDS)  
CONTROLS  
RESISTANCE VS TIME

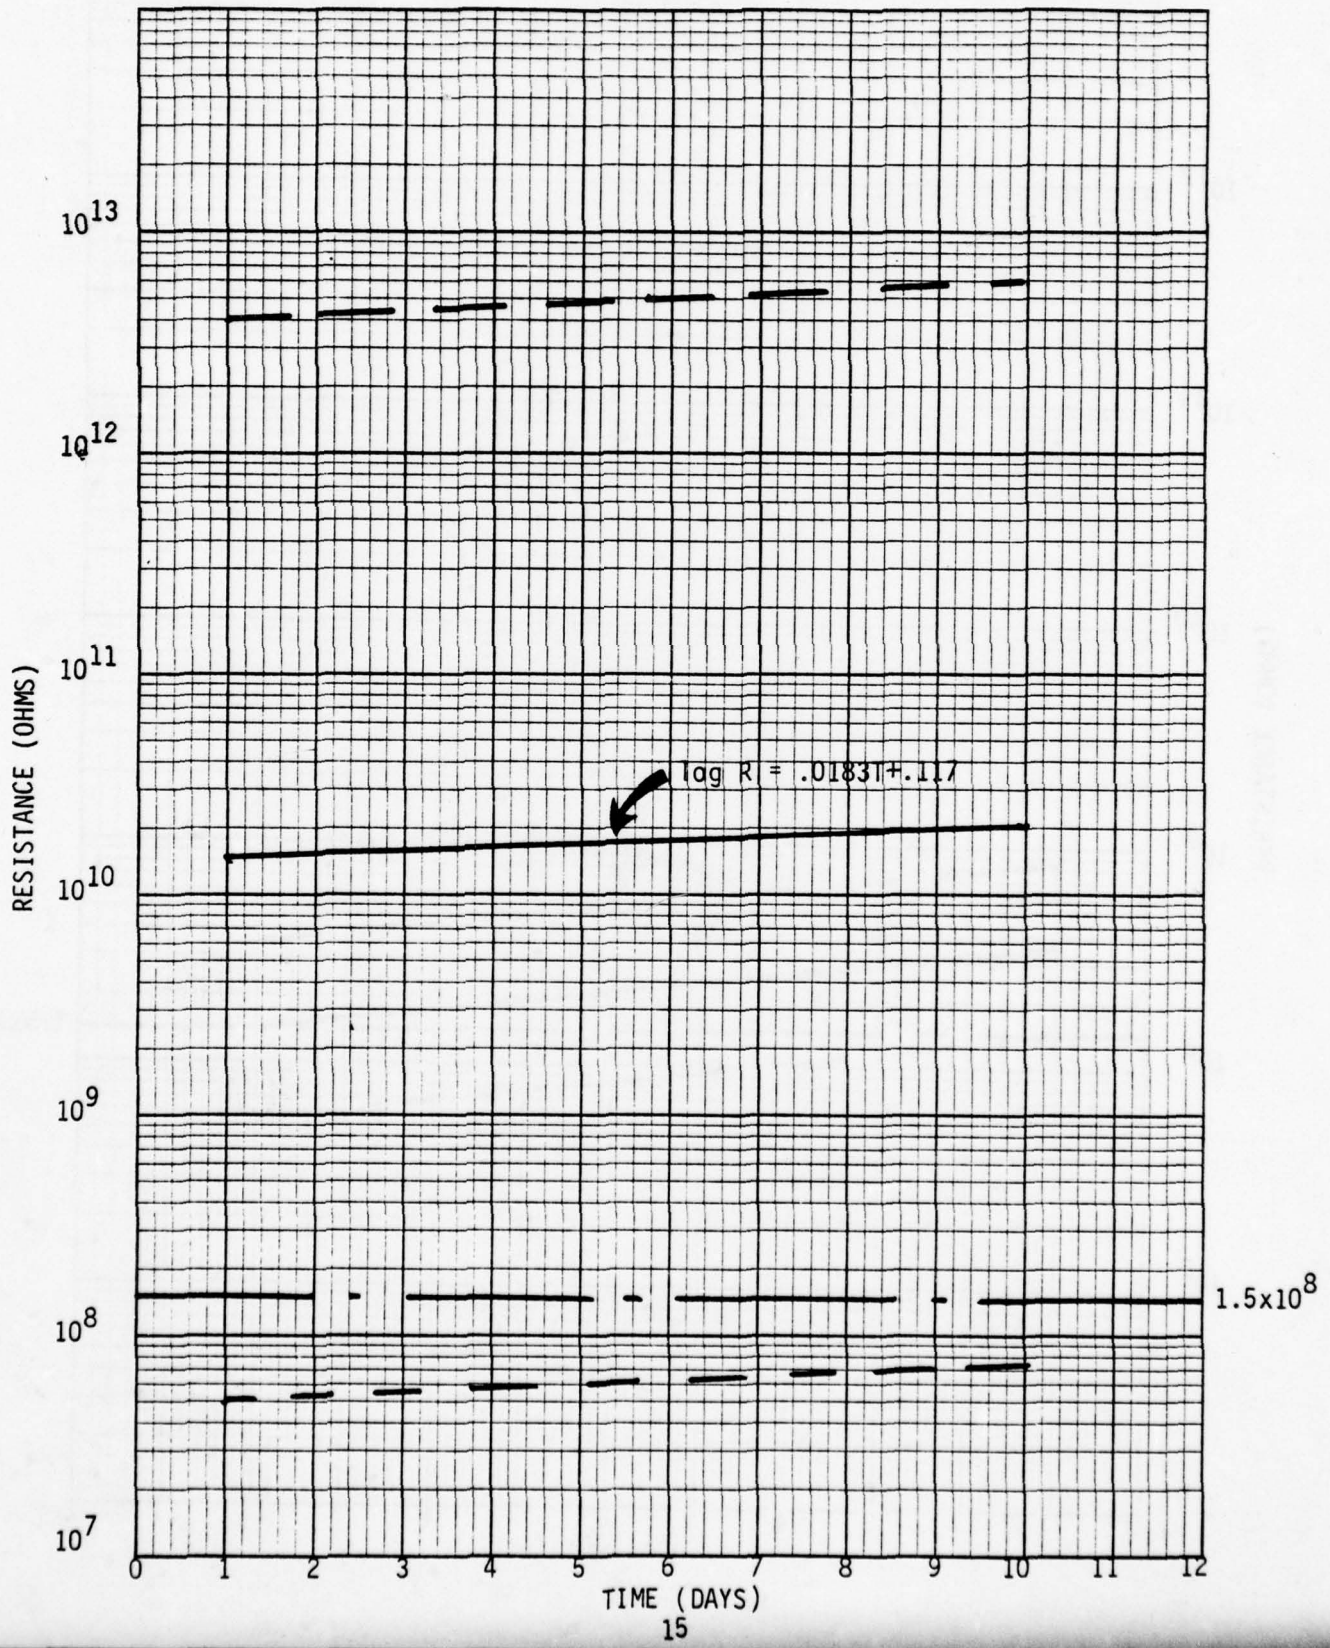


FIGURE 5.

72 HOUR DELAY  
A FUSING FLUID, 0 VOLTS STRESS,  
CONFORMALLY COATED  
RESISTANCE VS TIME

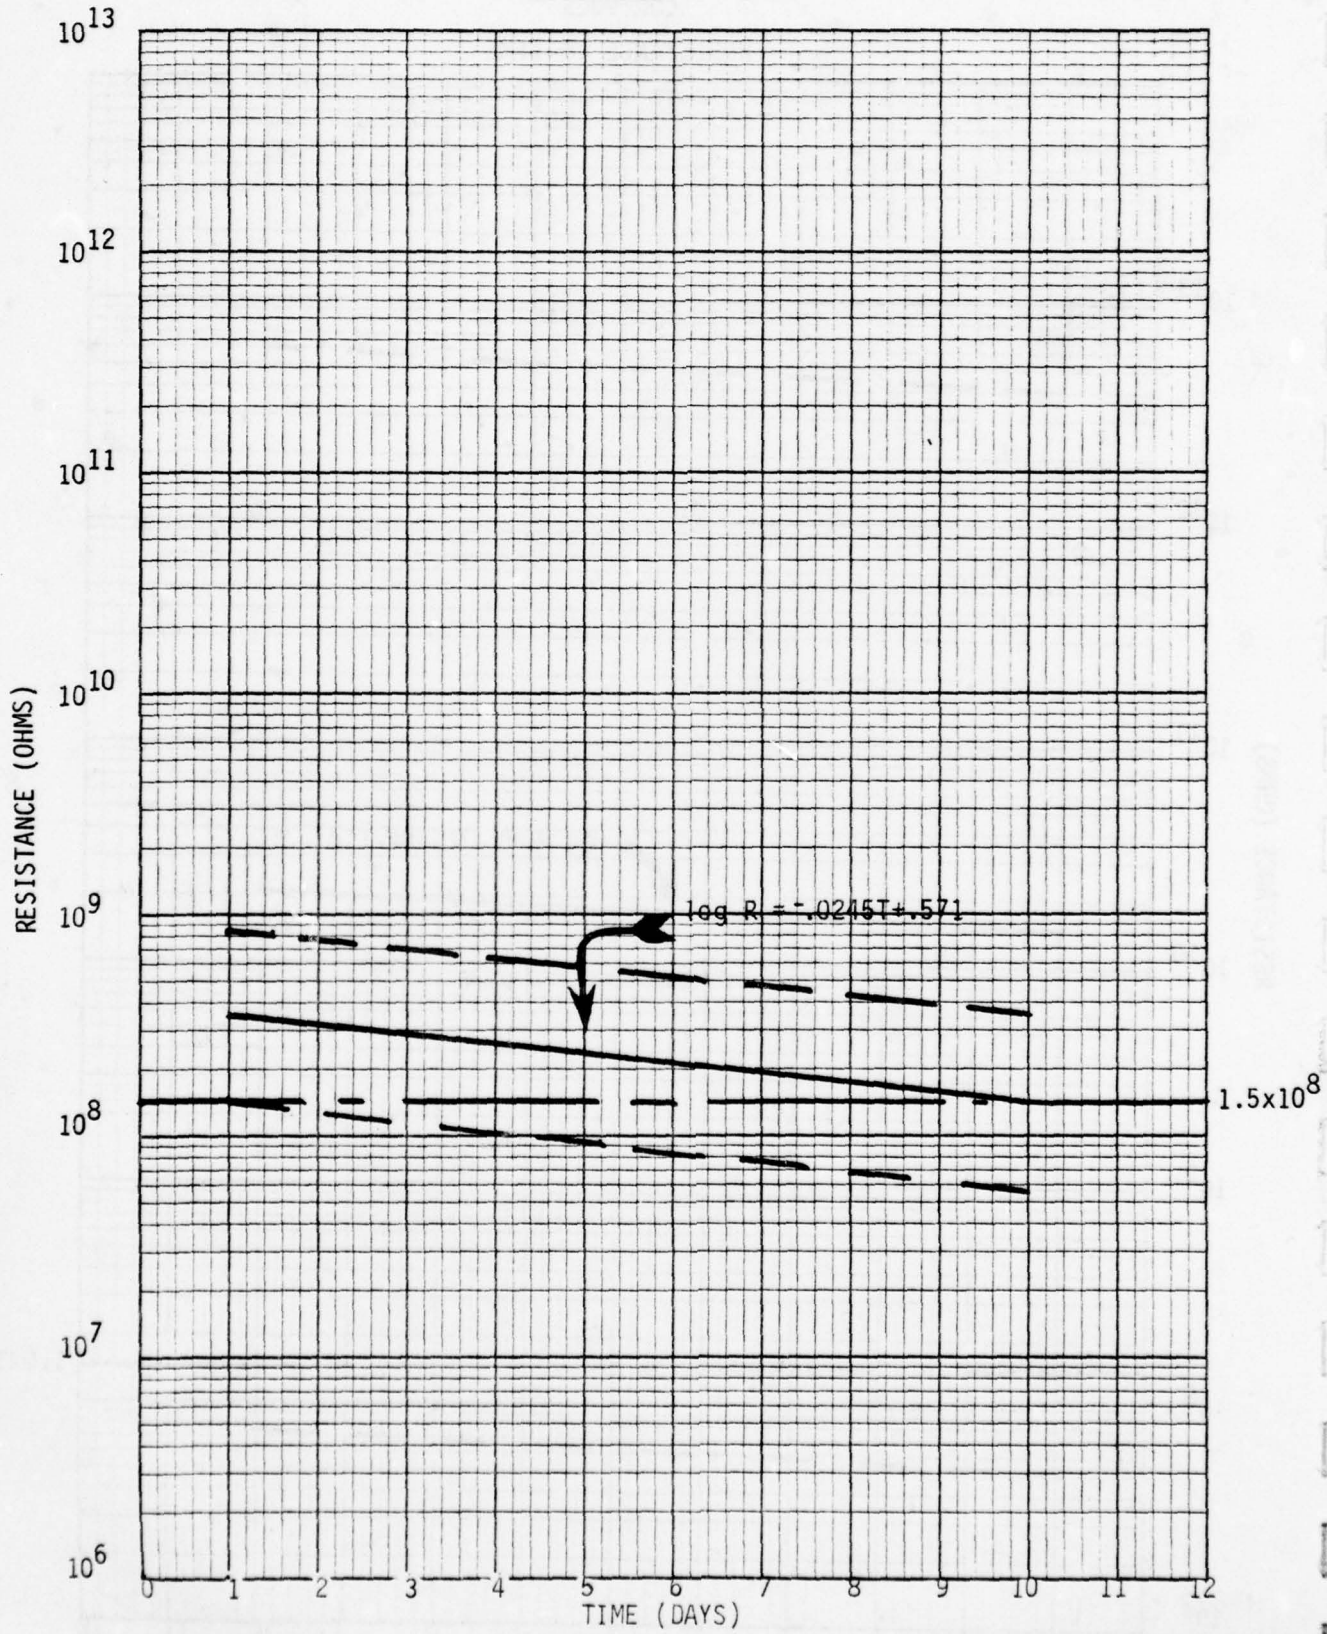


FIGURE 6.

72 HOUR DELAY  
A FUSING FLUID, 100 VOLTS STRESS,  
CONFORMALLY COATED  
RESISTANCE VS TIME

NAC TR-2259

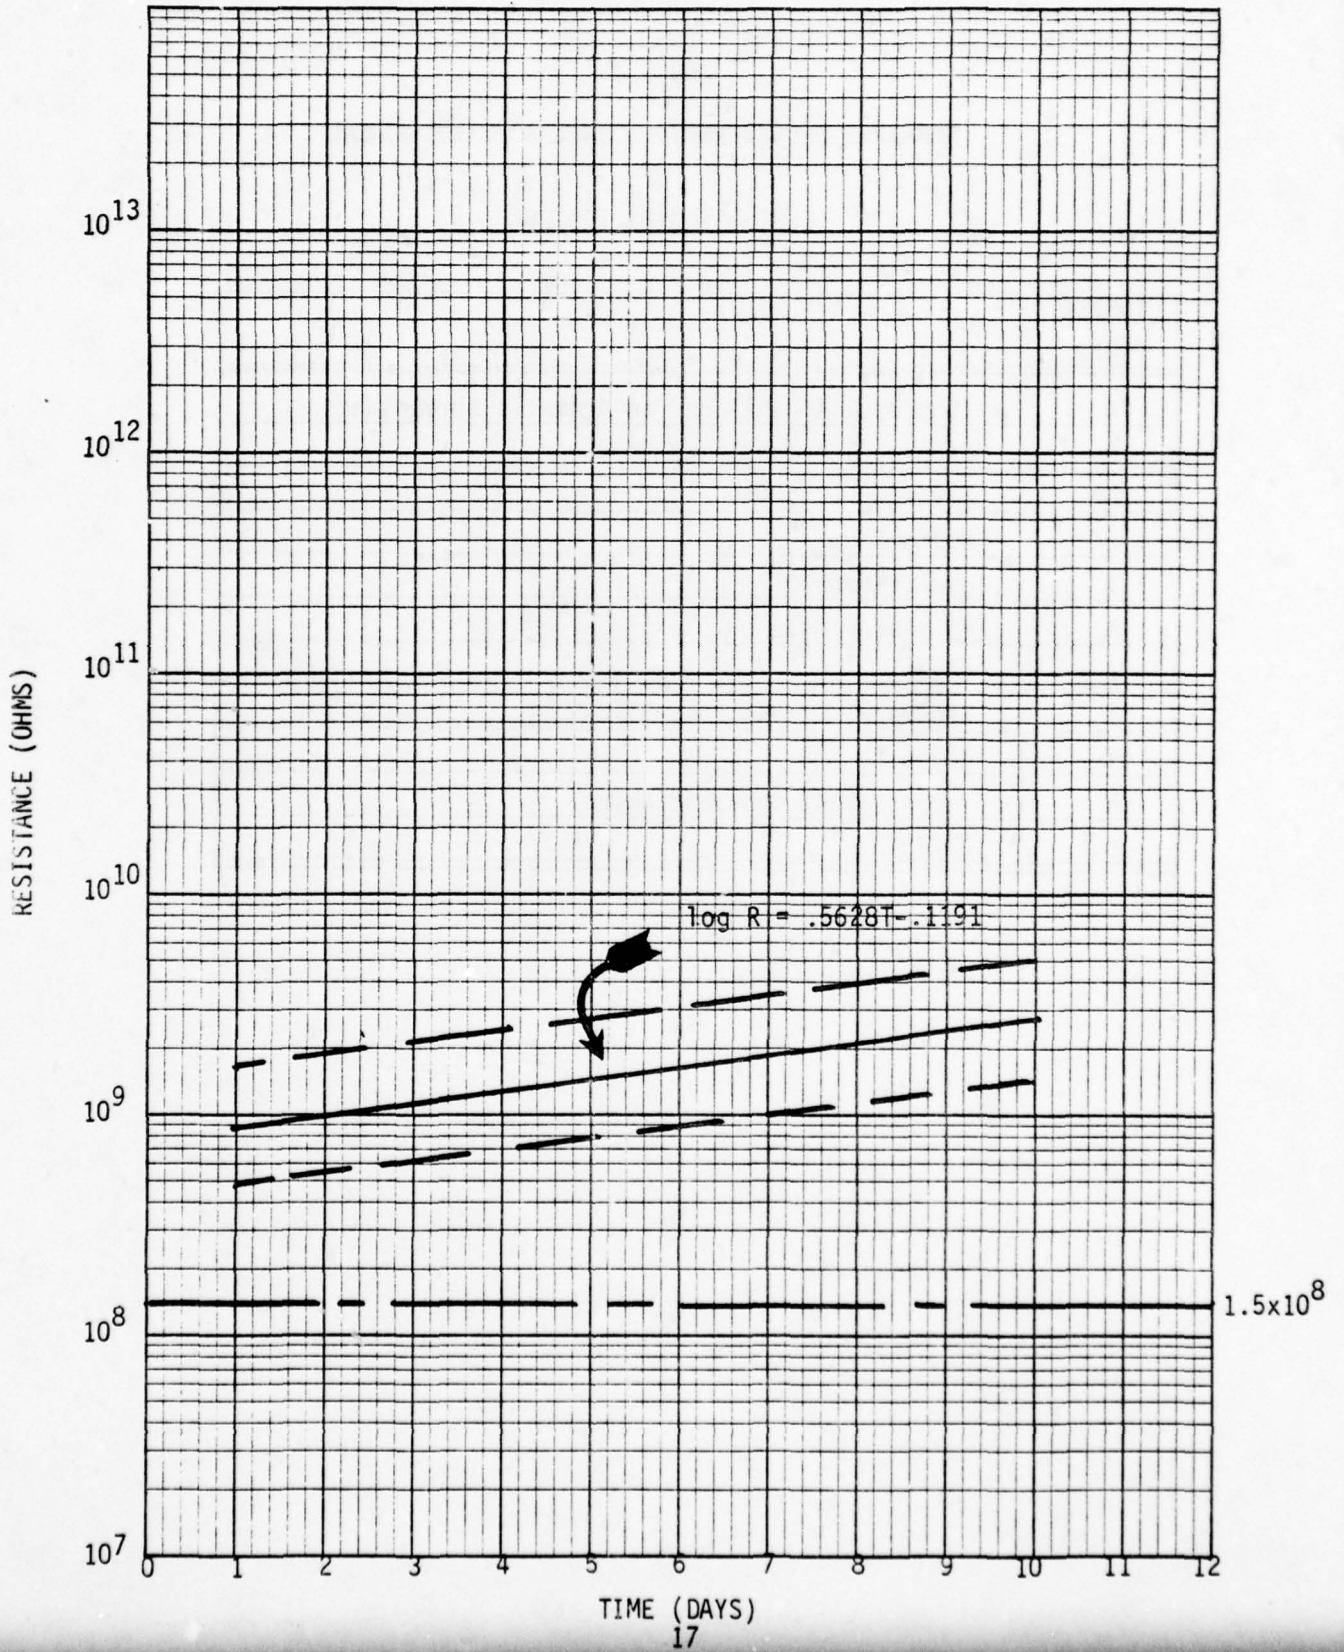


TABLE IV.  
INFRA-RED SPECTROPHOTOMETER CHARACTERIZATION  
OF  
FUSING FLUIDS TESTED

FUSING FLUID	RESULTS
A	Isopropyl Alcohol and an Aromatic Surfactant
B	Isopropyl Alcohol and Glycol
C	Glycol
F	Rosin Flux
I	Hydrocarbon Oil
K	Polyester Oil
J	Glycol
L	Isopropyl Alcohol and Glycol
M	Glycol
N	Isopropyl Alcohol and Glycol
O	Glycol

NAC TR-2259

## APPENDIX

1. Raw Data
2. Linear Regression Line Formula
3. MIL-P-28809 Ionic Contaminants Test
4. Equilibration Calculation
5. Materials
6. Equipment
7. Drawings

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (A)  
72 Hr. Delay  
CONFORMAL COATED  
0 VOLTS

FUSING FLUID  
TYPE (A)  
72 Hr. Delay  
CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS					Insulation Resistance - OHMS				
DAY	Spec.1	Spec.2 *	Spec.3	Spec.4	Control #1	Spec.1	Spec.2	Spec.3	Spec.4
3	$4.0 \times 10^8$	$5.25 \times 10^8$	$2.1 \times 10^8$	$2.7 \times 10^8$	$1.68 \times 10^{11}$	$10.4 \times 10^8$	$1.12 \times 10^9$	$9.0 \times 10^8$	$10.4 \times 10^8$
4	$2.6 \times 10^8$	$2.25 \times 10^8$	$1.66 \times 10^8$	$2 \times 10^8$	$1.2 \times 10^{11}$	$1.15 \times 10^9$	$1.15 \times 10^9$	$9.35 \times 10^8$	$1.06 \times 10^9$
5	$2.2 \times 10^8$	$1.4 \times 10^8$	$1.74 \times 10^8$	$2.1 \times 10^8$	$1.6 \times 10^{11}$	$1.6 \times 10^9$	$1.54 \times 10^9$	$1.34 \times 10^9$	$1.52 \times 10^9$
6	$2.73 \times 10^8$	$2.25 \times 10^8$	$3.15 \times 10^8$	$3.7 \times 10^8$	$1.53 \times 10^{11}$	$2.8 \times 10^9$	$2.3 \times 10^9$	$2.13 \times 10^9$	$2.33 \times 10^9$
7	$1.76 \times 10^8$	$1.34 \times 10^8$	$2 \times 10^8$	$1.6 \times 10^8$	$1.02 \times 10^{11}$	$2.25 \times 10^9$	$1.86 \times 10^9$	$1.74 \times 10^9$	$2 \times 10^9$
10	$1.58 \times 10^8$	$8.5 \times 10^7$	$1.88 \times 10^8$	$1.62 \times 10^8$	$8.6 \times 10^{10}$	$2.8 \times 10^9$	$2.1 \times 10^9$	$2.2 \times 10^9$	$2.43 \times 10^9$
* Faulty Specimen FUSING FLUID TYPE (A) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (A) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control #2	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$3.65 \times 10^{10}$	$5.1 \times 10^{10}$	$5.0 \times 10^{10}$	$2.2 \times 10^{10}$	$1.8 \times 10^9$	$3.75 \times 10^{10}$	$3.35 \times 10^{10}$	$1.1 \times 10^{10}$	$3.4 \times 10^{10}$
4	$3 \times 10^{10}$	$3.95 \times 10^{10}$	$3.85 \times 10^{10}$	$1.04 \times 10^{10}$	$1.15 \times 10^9$	$3 \times 10^{10}$	$2.45 \times 10^{10}$	$6.85 \times 10^9$	$2.6 \times 10^{10}$
5	$3.5 \times 10^{10}$	$4.1 \times 10^{10}$	$4.1 \times 10^{10}$	$1.15 \times 10^{10}$	$1.1 \times 10^9$	$3.3 \times 10^{10}$	$2.9 \times 10^{10}$	$8.85 \times 10^9$	$2.85 \times 10^{10}$
6	$3.35 \times 10^{10}$	$3.75 \times 10^{10}$	$3.7 \times 10^{10}$	$8.0 \times 10^9$	$9 \times 10^8$	$2.83 \times 10^{10}$	$2.23 \times 10^{10}$	$9.6 \times 10^9$	$2.25 \times 10^{10}$
7	$2.95 \times 10^{10}$	$3.2 \times 10^{10}$	$3.4 \times 10^{10}$	$8.5 \times 10^9$	$8.8 \times 10^8$	$2.8 \times 10^{10}$	$2.3 \times 10^{10}$	$1.1 \times 10^{10}$	$2.4 \times 10^{10}$
10	$2.5 \times 10^{10}$	$2.6 \times 10^{10}$	$2.78 \times 10^{10}$	$6.8 \times 10^9$	$2.43 \times 10^{10}$	$2.2 \times 10^{10}$	$1.42 \times 10^{10}$	$2.2 \times 10^{10}$	$2.2 \times 10^{10}$

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (B)  
72 Hr. Delay

FUSING FLUID  
TYPE (B)  
72 Hr. Delay

CONFORMAL COATED  
0 VOLTS

CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#3	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$2.9 \times 10^9$	$3.1 \times 10^9$	$3.5 \times 10^9$	$3.9 \times 10^9$	$5.5 \times 10^{10}$	$5.25 \times 10^9$	$5.25 \times 10^9$	$5.4 \times 10^9$	$5.5 \times 10^9$
4	$2.35 \times 10^9$	$2.4 \times 10^9$	$2.65 \times 10^9$	$2.95 \times 10^9$	$2.1 \times 10^{10}$	$3.8 \times 10^9$	$4.7 \times 10^9$	$4.6 \times 10^9$	$4.7 \times 10^9$
5	$3.35 \times 10^9$	$3.35 \times 10^9$	$3.5 \times 10^9$	$3.9 \times 10^9$	$2.1 \times 10^{10}$	$6 \times 10^9$	$6.4 \times 10^9$	$6.3 \times 10^9$	$6.35 \times 10^9$
6	$3.0 \times 10^9$	$2.85 \times 10^9$	$2.93 \times 10^9$	$3.13 \times 10^9$	$1.06 \times 10^{10}$	$4.93 \times 10^9$	$5.3 \times 10^9$	$5.2 \times 10^9$	$5.1 \times 10^9$
7	$3.2 \times 10^9$	$3.05 \times 10^9$	$3.28 \times 10^9$	$3.2 \times 10^9$	$1.4 \times 10^{10}$	$6.4 \times 10^9$	$7 \times 10^9$	$6.85 \times 10^9$	$6.85 \times 10^9$
10	$3.45 \times 10^9$	$3.3 \times 10^9$	$3.3 \times 10^9$	$3.85 \times 10^9$	$1.58 \times 10^{10}$	$7 \times 10^9$	$8.5 \times 10^9$	$7.9 \times 10^9$	$9.1 \times 10^9$
FUSING FLUID TYPE (B) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (B) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$2.6 \times 10^{10}$	$1.14 \times 10^{10}$	$2.9 \times 10^{10}$	$3.9 \times 10^{10}$		$4.25 \times 10^{10}$	$4.5 \times 10^{10}$	$4.9 \times 10^{10}$	$5.9 \times 10^9$
4	$2.4 \times 10^{10}$	$1.02 \times 10^{10}$	$3.7 \times 10^9$	$3.2 \times 10^{10}$		$2.75 \times 10^{10}$	$3.5 \times 10^{10}$	$4 \times 10^{10}$	$1.5 \times 10^{10}$
5	$3.25 \times 10^{10}$	$1.2 \times 10^{10}$	$4 \times 10^9$	$3.45 \times 10^{10}$		$1.6 \times 10^{10}$	$3.4 \times 10^{10}$	$4 \times 10^{10}$	$5.2 \times 10^9$
6	$1.86 \times 10^{10}$	$7.5 \times 10^9$	$1.8 \times 10^{10}$	$2.55 \times 10^{10}$		$1.15 \times 10^{10}$	$2 \times 10^{10}$	$3.1 \times 10^{10}$	$4.6 \times 10^9$
7	$3 \times 10^{10}$	$0.93 \times 10^{10}$	$2.73 \times 10^{10}$	$3 \times 10^{10}$		$2.15 \times 10^{10}$	$2.85 \times 10^{10}$	$3.25 \times 10^{10}$	$2.7 \times 10^9$
10	$2.75 \times 10^{10}$	$1 \times 10^{10}$	$2.7 \times 10^{10}$	$2.7 \times 10^{10}$		$2.55 \times 10^{10}$	$2.45 \times 10^{10}$	$3.2 \times 10^{10}$	$1.86 \times 10^{10}$

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (C)  
72 Hr. Delay  
CONFORMAL COATED  
0 VOLTS  
Insulation Resistance - OHMS

FUSING FLUID  
TYPE (C)  
72 Hr. Delay  
CONFORMAL COATED  
100 VOLTS  
Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$4.35 \times 10^{11}$	$2.35 \times 10^{11}$	$4.0 \times 10^{11}$	$4.85 \times 10^{11}$		$4.25 \times 10^{11}$	$3.75 \times 10^{10}$	$8.6 \times 10^{10}$	$4.5 \times 10^{11}$
4	$3.7 \times 10^{11}$	$2.25 \times 10^{11}$	$3.4 \times 10^{11}$	$3.9 \times 10^{11}$		$3.3 \times 10^{11}$	$2 \times 10^{10}$	$4.35 \times 10^{10}$	$2.95 \times 10^{11}$
5	$3.6 \times 10^{11}$	$2.8 \times 10^{11}$	$3.15 \times 10^{11}$	$3.7 \times 10^{11}$		$3.15 \times 10^{11}$	$8 \times 10^{10}$	$4.35 \times 10^{10}$	$3.5 \times 10^{11}$
6	$2.65 \times 10^{11}$	$1.53 \times 10^{11}$	$2.33 \times 10^{11}$	$2.7 \times 10^{11}$		$2.13 \times 10^{11}$	$8.4 \times 10^{10}$	$3.45 \times 10^{10}$	$2.57 \times 10^{11}$
7	$2.65 \times 10^{11}$	$1.7 \times 10^{11}$	$2.3 \times 10^{11}$	$2.3 \times 10^{11}$		$1.94 \times 10^{11}$	$9.5 \times 10^{10}$	$5 \times 10^{10}$	$2.57 \times 10^{11}$
10	$2.25 \times 10^{11}$	$1.6 \times 10^{11}$	$1.9 \times 10^{11}$	$2.2 \times 10^{11}$		$1.62 \times 10^{11}$	$6.7 \times 10^{10}$	$2.2 \times 10^{10}$	$2 \times 10^{11}$
FUSING FLUID TYPE (C) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (C) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$2.05 \times 10^{11}$	$2.9 \times 10^{11}$	$1.9 \times 10^{11}$	$1.6 \times 10^{11}$		$1.62 \times 10^{11}$	$5.8 \times 10^{10}$	$5 \times 10^{10}$	$6.65 \times 10^{10}$
4	$1.48 \times 10^{11}$	$2.2 \times 10^{11}$	$1.56 \times 10^{11}$	$1.2 \times 10^{11}$		$1.26 \times 10^{11}$	$7.35 \times 10^{10}$	$5.2 \times 10^{10}$	$2.7 \times 10^{10}$
5	$1.32 \times 10^{11}$	$1.95 \times 10^{11}$	$1.3 \times 10^{11}$	$1.13 \times 10^{11}$		$1.1 \times 10^{11}$	$6 \times 10^{10}$	$3.8 \times 10^{10}$	$5.5 \times 10^{10}$
6	$1 \times 10^{11}$	$1.46 \times 10^{11}$	$9.6 \times 10^{10}$	$8.8 \times 10^{10}$		$8.4 \times 10^{10}$	$5.5 \times 10^{10}$	$3.3 \times 10^{10}$	$3.7 \times 10^{10}$
7	$0.94 \times 10^{11}$	$1.38 \times 10^{11}$	$9.2 \times 10^{10}$	$8.4 \times 10^{10}$		$8.1 \times 10^{10}$	$4.6 \times 10^{10}$	$3.4 \times 10^{10}$	$4.1 \times 10^{10}$
10	$6.85 \times 10^{10}$	$0.97 \times 10^{11}$	$6.1 \times 10^{10}$	$6 \times 10^{10}$		$5.9 \times 10^{10}$	$3.65 \times 10^{10}$	$2.35 \times 10^{10}$	$4.5 \times 10^{10}$

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (A)  
168 Hr. Delay

CONFORMAL COATED  
0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID  
TYPE (A)  
168 Hr. Delay

CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#1	Spec. 1	Spec. 2	Spec. 3	Spec. 4
1	$1.2 \times 10^9$	$1.7 \times 10^9$	$4.4 \times 10^9$	$5.2 \times 10^9$	$4 \times 10^{10}$	$6.5 \times 10^9$	$1.18 \times 10^{10}$	$5.7 \times 10^9$	$6.3 \times 10^9$
2	$0.96 \times 10^9$	$1.2 \times 10^9$	$2.6 \times 10^9$	$4.6 \times 10^{10}$	$3.3 \times 10^{10}$	$6 \times 10^9$	$8.8 \times 10^9$	$8.5 \times 10^9$	$6.7 \times 10^9$
3	$1.3 \times 10^9$	$1.52 \times 10^9$	$2.8 \times 10^9$	$6.9 \times 10^9$	$3.3 \times 10^{10}$	$7.5 \times 10^9$	$1 \times 10^{10}$	$1.02 \times 10^{10}$	$8.9 \times 10^9$
7	$1.03 \times 10^9$	$1.4 \times 10^9$	$1.27 \times 10^9$	$3.3 \times 10^9$	$8.5 \times 10^9$	$3.3 \times 10^9$	$2.75 \times 10^9$	$3.7 \times 10^9$	$3 \times 10^9$
8	$8.8 \times 10^9$	$9.6 \times 10^9$	$9 \times 10^9$	$1.64 \times 10^{10}$	$4.85 \times 10^{10}$	$1.86 \times 10^{10}$	$2.1 \times 10^{10}$	$2.25 \times 10^{10}$	$2.1 \times 10^{10}$
9	$3.25 \times 10^9$	$2.45 \times 10^9$	$3.4 \times 10^9$	$9.4 \times 10^9$	$9.4 \times 10^9$	$8.5 \times 10^9$	$9.7 \times 10^9$	$1.09 \times 10^{10}$	$.98 \times 10^{10}$
10	$1.9 \times 10^9$	$1.8 \times 10^9$	$2.55 \times 10^9$	$6.6 \times 10^9$	$7.2 \times 10^9$	$6.1 \times 10^9$	$7 \times 10^9$	$8 \times 10^9$	$7 \times 10^9$
<p>FUSING FLUID TYPE (A) 168 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS</p>					<p>FUSING FLUID TYPE (A) 168 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS</p>				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#2	Spec. 1	Spec. 2	Spec. 3	Spec. 4
1	$2.8 \times 10^{11}$	$2.8 \times 10^{11}$	$2.4 \times 10^{11}$	$2.1 \times 10^{11}$	$2.9 \times 10^{11}$	$1.2 \times 10^{11}$	$9.5 \times 10^{10}$	$9.6 \times 10^{10}$	$9 \times 10^{10}$
2	$1.4 \times 10^{11}$	$1.1 \times 10^{11}$	$9 \times 10^{10}$	$9.6 \times 10^{10}$	$1.37 \times 10^{11}$	$6.2 \times 10^{10}$	$6 \times 10^{10}$	$6.2 \times 10^{10}$	$5.7 \times 10^{10}$
3	$7.8 \times 10^{10}$	$8.1 \times 10^{10}$	$6.6 \times 10^{10}$	$7.4 \times 10^{10}$	$8.3 \times 10^{10}$	$5 \times 10^{10}$	$5.4 \times 10^{10}$	$5.2 \times 10^{10}$	$5.1 \times 10^{10}$
7	$1.22 \times 10^{10}$	$1.18 \times 10^{10}$	$1.02 \times 10^{10}$	$1 \times 10^{10}$	$1.2 \times 10^{10}$	$6 \times 10^9$	$7 \times 10^9$	$5.8 \times 10^9$	$5.7 \times 10^9$
8	$2.45 \times 10^{10}$	$2.4 \times 10^{10}$	$2.1 \times 10^{10}$	$2.6 \times 10^{10}$	$2.6 \times 10^{10}$	$2.1 \times 10^{10}$	$2.2 \times 10^{10}$	$1.92 \times 10^{10}$	$2 \times 10^{10}$
9	$1.44 \times 10^{10}$	$1.4 \times 10^{10}$	$1.2 \times 10^{10}$	$1.5 \times 10^{10}$	$1.64 \times 10^{10}$	$1.05 \times 10^{10}$	$1.08 \times 10^{10}$	$.93 \times 10^{10}$	$.96 \times 10^{10}$
10	$9.9 \times 10^9$	$9.6 \times 10^9$	$8.25 \times 10^9$	$1.04 \times 10^{10}$	$1.24 \times 10^{10}$	$7.8 \times 10^9$	$8.2 \times 10^9$	$6.75 \times 10^9$	$6.65 \times 10^9$

NAC TR-2259

RAW DATA

FUSING FLUID  
TYPE (B)  
168 Hr. Delay

CONFORMAL COATED  
0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID  
TYPE (B)  
168 Hr. Delay

CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS

DAY	FUSING FLUID TYPE (B) 168 Hr. Delay CONFORMAL COATED 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (B) 168 Hr. Delay CONFORMAL COATED 100 VOLTS Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#3	Spec. 1	Spec. 2	Spec. 3	Spec. 4
1	4.6x10 <sup>9</sup>	1.6x10 <sup>9</sup>	5.9x10 <sup>8</sup>	2.7x10 <sup>9</sup>	7.6x10 <sup>10</sup>	2.1x10 <sup>9</sup>	2.8x10 <sup>9</sup>	4.4x10 <sup>9</sup>	2.1x10 <sup>9</sup>
2	3.9x10 <sup>9</sup>	1.4x10 <sup>9</sup>	5.9x10 <sup>8</sup>	3.2x10 <sup>9</sup>	5.5x10 <sup>10</sup>	2.4x10 <sup>9</sup>	3.5x10 <sup>9</sup>	5.7x10 <sup>9</sup>	2.6x10 <sup>9</sup>
3	6.8x10 <sup>9</sup>	4.4x10 <sup>9</sup>	1.8x10 <sup>9</sup>	5.5x10 <sup>9</sup>	6x10 <sup>10</sup>	4x10 <sup>9</sup>	5.3x10 <sup>9</sup>	7.7x10 <sup>9</sup>	3.5x10 <sup>9</sup>
7	1.22x10 <sup>9</sup>	6.3x10 <sup>8</sup>	3.3x10 <sup>8</sup>	6.5x10 <sup>8</sup>	9x10 <sup>10</sup>	1.18x10 <sup>9</sup>	1.52x10 <sup>9</sup>	1.88x10 <sup>9</sup>	1.07x10 <sup>9</sup>
8	1.6x10 <sup>10</sup>	1.4x10 <sup>10</sup>	1.17x10 <sup>10</sup>	1.18x10 <sup>10</sup>	3.8x10 <sup>11</sup>	1.55x10 <sup>10</sup>	1.76x10 <sup>10</sup>	1.64x10 <sup>10</sup>	1.45x10 <sup>10</sup>
9	6.25x10 <sup>9</sup>	5.5x10 <sup>9</sup>	3.85x10 <sup>9</sup>	3.75x10 <sup>9</sup>	1.06x10 <sup>11</sup>	5.5x10 <sup>9</sup>	6.4x10 <sup>9</sup>	6.4x10 <sup>9</sup>	5x10 <sup>9</sup>
10	4.4x10 <sup>9</sup>	3.8x10 <sup>9</sup>	2.45x10 <sup>9</sup>	2.65x10 <sup>9</sup>	6.7x10 <sup>10</sup>	3.4x10 <sup>9</sup>	4.2x10 <sup>9</sup>	4.4x10 <sup>9</sup>	3.1x10 <sup>9</sup>
	FUSING FLUID TYPE (B) 168 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (B) 168 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS			
DAY	FUSING FLUID TYPE (B) 168 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (B) 168 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#4	Spec. 1	Spec. 2	Spec. 3	Spec. 4
1	2.4x10 <sup>11</sup>	2.4x10 <sup>11</sup>	2.5x10 <sup>11</sup>	4.7x10 <sup>10</sup>	9.3x10 <sup>10</sup>	1.8x10 <sup>11</sup>	1.6x10 <sup>11</sup>	1.08x10 <sup>11</sup>	1.56x10 <sup>11</sup>
2	1.05x10 <sup>11</sup>	1.24x10 <sup>11</sup>	1.32x10 <sup>11</sup>	3.25x10 <sup>10</sup>	8.6x10 <sup>10</sup>	9x10 <sup>10</sup>	8.7x10 <sup>10</sup>	8.9x10 <sup>10</sup>	1.14x10 <sup>11</sup>
3	8.5x10 <sup>10</sup>	0.99x10 <sup>11</sup>	1.04x10 <sup>11</sup>	3.1x10 <sup>10</sup>	7.9x10 <sup>10</sup>	7x10 <sup>10</sup>	6.2x10 <sup>10</sup>	6.8x10 <sup>10</sup>	8.6x10 <sup>10</sup>
7	8.6x10 <sup>9</sup>	8.75x10 <sup>9</sup>	9.5x10 <sup>9</sup>	5.25x10 <sup>9</sup>	5x10 <sup>10</sup>	8.5x10 <sup>9</sup>	8.5x10 <sup>9</sup>	8.4x10 <sup>9</sup>	10x10 <sup>9</sup>
8	4.6x10 <sup>10</sup>	5.4x10 <sup>10</sup>	6x10 <sup>10</sup>	4.8x10 <sup>10</sup>	1.1x10 <sup>12</sup>	6.1x10 <sup>10</sup>	4.6x10 <sup>10</sup>	5.5x10 <sup>10</sup>	6.75x10 <sup>10</sup>
9	2x10 <sup>10</sup>	2.35x10 <sup>10</sup>	2.6x10 <sup>10</sup>	1.77x10 <sup>10</sup>	1.12x10 <sup>11</sup>	2.3x10 <sup>10</sup>	2x10 <sup>10</sup>	2.15x10 <sup>10</sup>	2.6x10 <sup>10</sup>
10	1.32x10 <sup>10</sup>	1.52x10 <sup>10</sup>	1.68x10 <sup>10</sup>	1.12x10 <sup>10</sup>	6.5x10 <sup>10</sup>	1.57x10 <sup>10</sup>	1.35x10 <sup>10</sup>	1.52x10 <sup>10</sup>	1.8x10 <sup>10</sup>

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (C)  
168 Hr. Delay  
CONFORMAL COATED  
0 VOLTS

FUSING FLUID  
TYPE (C)  
168 Hr. Delay  
CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS					Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4	
1	$1.86 \times 10^{12}$	$5.6 \times 10^{11}$	$1.24 \times 10^{12}$	$6.3 \times 10^{10}$	$5.4 \times 10^{10}$	$6.7 \times 10^{10}$	$1.34 \times 10^{12}$	$1.84 \times 10^{12}$	
2	$1.2 \times 10^{12}$	$6.4 \times 10^{11}$	$9 \times 10^{11}$	$6.5 \times 10^{10}$	$1.74 \times 10^{11}$	$2.9 \times 10^{11}$	$8.5 \times 10^{11}$	$1.3 \times 10^{12}$	
3	$9.9 \times 10^{11}$	$8.6 \times 10^{11}$	$8 \times 10^{11}$	$7.3 \times 10^{10}$	$3.3 \times 10^{11}$	$5.5 \times 10^{11}$	$7 \times 10^{11}$	$8.8 \times 10^{11}$	
7	$1.13 \times 10^{11}$	$1.23 \times 10^{11}$	$1.24 \times 10^{11}$	$0.97 \times 10^{11}$	$1.35 \times 10^{11}$	$1.25 \times 10^{11}$	$1.7 \times 10^{11}$	$1.5 \times 10^{11}$	
8	$5.5 \times 10^{11}$	$5.9 \times 10^{11}$	$5.75 \times 10^{11}$	$5.1 \times 10^{11}$	$5.5 \times 10^{11}$	$5.6 \times 10^{11}$	$6.4 \times 10^{11}$	$6.1 \times 10^{11}$	
9	$2.65 \times 10^{11}$	$2.7 \times 10^{11}$	$2.75 \times 10^{11}$	$2.15 \times 10^{11}$	$2.75 \times 10^{11}$	$2.6 \times 10^{11}$	$3.25 \times 10^{11}$	$3.1 \times 10^{11}$	
10	$1.85 \times 10^{11}$	$2.1 \times 10^{11}$	$1.97 \times 10^{11}$	$1.6 \times 10^{11}$	$1.92 \times 10^{11}$	$1.72 \times 10^{11}$	$2.25 \times 10^{11}$	$2.1 \times 10^{11}$	
FUSING FLUID TYPE (C) 168 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (C) 168 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4	
1	$0.97 \times 10^{12}$	$1.09 \times 10^{12}$	$1.2 \times 10^{12}$	$1.07 \times 10^{12}$	$8.6 \times 10^{11}$	$7.2 \times 10^{11}$	$7.5 \times 10^{11}$	$2.25 \times 10^{11}$	
2	$5.6 \times 10^{11}$	$5.8 \times 10^{11}$	$5.8 \times 10^{11}$	$5.3 \times 10^{11}$	$4.5 \times 10^{11}$	$3.5 \times 10^{11}$	$3.7 \times 10^{11}$	$1.1 \times 10^{10}$	
3	$3.4 \times 10^{11}$	$3.3 \times 10^{11}$	$3.5 \times 10^{11}$	$3.2 \times 10^{11}$	$2.4 \times 10^{11}$	$1.68 \times 10^{11}$	$1.7 \times 10^{11}$	$1.4 \times 10^{10}$	
7	$4 \times 10^{10}$	$3.4 \times 10^{10}$	$3.9 \times 10^{10}$	$3.5 \times 10^{10}$	$3.45 \times 10^{10}$	$2.65 \times 10^{10}$	$3 \times 10^{10}$	$2.45 \times 10^{10}$	
8	$1.54 \times 10^{11}$	$1.27 \times 10^{11}$	$1.32 \times 10^{11}$	$1.26 \times 10^{11}$	$1.06 \times 10^{11}$	$6 \times 10^{10}$	$6.8 \times 10^{10}$	$5 \times 10^{10}$	
9	$7.2 \times 10^{10}$	$4.85 \times 10^{10}$	$6.3 \times 10^{10}$	$5.7 \times 10^{10}$	$4.4 \times 10^{10}$	$1.9 \times 10^{10}$	$2.2 \times 10^{10}$	$1.25 \times 10^{10}$	
10	$5.3 \times 10^{10}$	$3.5 \times 10^{10}$	$4.4 \times 10^{10}$	$4 \times 10^{10}$	$3.15 \times 10^{10}$	$1.4 \times 10^{10}$	$1.66 \times 10^{10}$	$1.03 \times 10^{10}$	

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (F)  
72 Hr. Delay

FUSING FLUID  
TYPE (F)  
72 Hr. Delay

CONFORMAL COATED  
0 VOLTS

CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#1	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$7 \times 10^{10}$	$6.1 \times 10^{10}$	$7.9 \times 10^{10}$	$5.8 \times 10^{10}$	$1.79 \times 10^{10}$	$5.7 \times 10^{10}$	$6.3 \times 10^{10}$	$6.6 \times 10^{10}$	$5.5 \times 10^{10}$
4	$4.45 \times 10^{10}$	$3.9 \times 10^{10}$	$4.5 \times 10^{10}$	$3.6 \times 10^{10}$	$1.06 \times 10^{10}$	$3.65 \times 10^{10}$	$3.65 \times 10^{10}$	$4 \times 10^{10}$	$3.25 \times 10^{10}$
5	$3.35 \times 10^{10}$	$2.9 \times 10^{10}$	$3.1 \times 10^{10}$	$2.55 \times 10^{10}$	$7.7 \times 10^9$	$2.8 \times 10^{10}$	$2.6 \times 10^{10}$	$2.8 \times 10^{10}$	$2.3 \times 10^{10}$
6	$2.7 \times 10^{10}$	$2.25 \times 10^{10}$	$2.35 \times 10^{10}$	$1.96 \times 10^{10}$	$6 \times 10^9$	$2.1 \times 10^{10}$	$1.92 \times 10^{10}$	$2.2 \times 10^{10}$	$1.78 \times 10^{10}$
7	$2.5 \times 10^{10}$	$2 \times 10^{10}$	$1.96 \times 10^{10}$	$1.7 \times 10^{10}$	$5.4 \times 10^9$	$1.84 \times 10^{10}$	$1.64 \times 10^{10}$	$1.84 \times 10^{10}$	$1.48 \times 10^{10}$
10	$1.66 \times 10^{10}$	$1.36 \times 10^{10}$	$1.38 \times 10^{10}$	$1.2 \times 10^{10}$	$4.05 \times 10^9$	$1.5 \times 10^{10}$	$1.4 \times 10^{10}$	$1.56 \times 10^{10}$	$1.2 \times 10^{10}$

FUSING FLUID  
TYPE (F)  
72 Hr. Delay

FUSING FLUID  
TYPE (F)  
72 Hr. Delay

SOLDER MASK  
0 VOLTS

SOLDER MASK  
100 VOLTS

Insulation Resistance - OHMS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#2	Spec. 1	Spec. 2	Spec. 3	Spec. 4*
3	$6.4 \times 10^{11}$	$2.95 \times 10^{10}$	$3.85 \times 10^{10}$	$2.2 \times 10^{10}$	$2.55 \times 10^{10}$	$3.75 \times 10^{10}$	$3.6 \times 10^{10}$	$4.65 \times 10^{10}$	$7.8 \times 10^8$
4	$1.62 \times 10^{11}$	$1.98 \times 10^{10}$	$2.55 \times 10^{10}$	$1.28 \times 10^{10}$	$1.58 \times 10^{10}$	$2.43 \times 10^{10}$	$2.37 \times 10^{10}$	$2.75 \times 10^{10}$	$9.8 \times 10^8$
5	$8.1 \times 10^{10}$	$1.52 \times 10^{10}$	$1.88 \times 10^{10}$	$5.4 \times 10^9$	$1.18 \times 10^{10}$	$1.9 \times 10^{10}$	$1.82 \times 10^{10}$	$1.98 \times 10^{10}$	$8.2 \times 10^8$
6	$6.2 \times 10^{10}$	$1.2 \times 10^{10}$	$1.52 \times 10^{10}$	$3.15 \times 10^9$	$9.5 \times 10^9$	$1.5 \times 10^{10}$	$1.46 \times 10^{10}$	$1.56 \times 10^{10}$	$6.6 \times 10^8$
7	$4.95 \times 10^{10}$	$1.04 \times 10^{10}$	$1.28 \times 10^{10}$	$2.75 \times 10^9$	$8 \times 10^9$	$1.3 \times 10^{10}$	$1.26 \times 10^{10}$	$1.3 \times 10^{10}$	$7 \times 10^8$
10	$5.6 \times 10^{10}$	$8.9 \times 10^9$	$1.06 \times 10^{10}$	$2.7 \times 10^9$	$5.7 \times 10^9$	$1.08 \times 10^{10}$	$1.06 \times 10^{10}$	$1.1 \times 10^{10}$	$8.6 \times 10^8$

\* Faulty Specimen

NAC TR-2259

RAW DATA

FUSING FLUID

TYPE (I)

72 Hr. Delay

CONFORMAL COATED

0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID

TYPE (I)

72 Hr. Delay

CONFORMAL COATED

100 VOLTS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$2.45 \times 10^{10}$	$5.5 \times 10^{10}$	$6.1 \times 10^{10}$	$4.95 \times 10^{10}$		$5.7 \times 10^{10}$	$4.8 \times 10^{10}$	$5.3 \times 10^{10}$	$2.8 \times 10^{10}$
4	$9.4 \times 10^9$	$3.4 \times 10^{10}$	$3.6 \times 10^{10}$	$2.95 \times 10^{10}$		$3.6 \times 10^{10}$	$2.95 \times 10^{10}$	$3.1 \times 10^{10}$	$1.5 \times 10^{10}$
5	$6.2 \times 10^9$	$2.5 \times 10^{10}$	$2.6 \times 10^{10}$	$2.08 \times 10^{10}$		$2.65 \times 10^{10}$	$2.12 \times 10^{10}$	$2.24 \times 10^{10}$	$1.36 \times 10^{10}$
6	$5.02 \times 10^9$	$1.8 \times 10^{10}$	$1.95 \times 10^{10}$	$1.55 \times 10^{10}$		$2.0 \times 10^{10}$	$1.64 \times 10^{10}$	$1.78 \times 10^{10}$	$1.16 \times 10^{10}$
7	$4.55 \times 10^9$	$1.52 \times 10^{10}$	$1.57 \times 10^{10}$	$1.19 \times 10^{10}$		$1.76 \times 10^{10}$	$1.4 \times 10^{10}$	$1.5 \times 10^{10}$	$9.95 \times 10^9$
10	$5.25 \times 10^9$	$1.11 \times 10^{10}$	$1.18 \times 10^{10}$	$8.7 \times 10^9$		$1.45 \times 10^{10}$	$1.11 \times 10^{10}$	$1.18 \times 10^{10}$	$6.3 \times 10^9$

FUSING FLUID

TYPE (I)

72 Hr. Delay

SOLDER MASK

0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID

TYPE (I)

72 Hr. Delay

SOLDER MASK

100 VOLTS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$2.45 \times 10^{10}$	$2.05 \times 10^{10}$	$1.62 \times 10^{10}$	$4.05 \times 10^{10}$		$3.8 \times 10^{10}$	$4.3 \times 10^{10}$	$3.2 \times 10^{10}$	$2.85 \times 10^{10}$
4	$1.7 \times 10^{10}$	$1.42 \times 10^{10}$	$11.4 \times 10^9$	$2.75 \times 10^{10}$		$2.6 \times 10^{10}$	$2.95 \times 10^{10}$	$2.2 \times 10^{10}$	$2.0 \times 10^{10}$
5	$1.27 \times 10^{10}$	$10.2 \times 10^9$	$8.5 \times 10^9$	$2.0 \times 10^{10}$		$2.0 \times 10^{10}$	$2.24 \times 10^{10}$	$1.66 \times 10^{10}$	$1.52 \times 10^{10}$
6	$9.8 \times 10^9$	$8.1 \times 10^9$	$6.7 \times 10^9$	$1.56 \times 10^{10}$		$1.64 \times 10^{10}$	$1.87 \times 10^{10}$	$1.41 \times 10^{10}$	$1.27 \times 10^{10}$
7	$8.3 \times 10^9$	$6.7 \times 10^9$	$5.6 \times 10^9$	$1.27 \times 10^{10}$		$1.44 \times 10^{10}$	$1.62 \times 10^{10}$	$1.23 \times 10^{10}$	$1.1 \times 10^{10}$
10	$6.65 \times 10^9$	$5.5 \times 10^9$	$4.7 \times 10^9$	$9.75 \times 10^9$		$1.17 \times 10^{10}$	$1.29 \times 10^{10}$	$10.0 \times 10^9$	$8.9 \times 10^9$

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (K)  
72 Hr. Delay  
CONFORMAL COATED  
0 VOLTS

FUSING FLUID  
TYPE (K)  
72 Hr. Delay  
CONFORMAL COATED  
100 VOLTS

DAY	Insulation Resistance - OHMS				Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$3.5 \times 10^{10}$	$7.5 \times 10^{10}$		$1.32 \times 10^{11}$	$9.7 \times 10^{10}$	$1.02 \times 10^{11}$	$1.06 \times 10^{11}$	$1.22 \times 10^{11}$
4	$9.9 \times 10^9$	$4.9 \times 10^{10}$		$7.8 \times 10^{10}$	$5.7 \times 10^{10}$	$6.0 \times 10^{10}$	$6.4 \times 10^{10}$	$7.0 \times 10^{10}$
5	$5.35 \times 10^9$	$3.6 \times 10^{10}$		$5.55 \times 10^{10}$	$4.0 \times 10^{10}$	$4.2 \times 10^{10}$	$4.55 \times 10^{10}$	$4.9 \times 10^{10}$
6	$1.6 \times 10^{10}$	$2.75 \times 10^{10}$		$4.15 \times 10^{10}$	$3.0 \times 10^{10}$	$3.2 \times 10^{10}$	$3.5 \times 10^{10}$	$3.6 \times 10^{10}$
7	$1.38 \times 10^{10}$	$2.25 \times 10^{10}$		$3.35 \times 10^{10}$	$2.5 \times 10^{10}$	$2.58 \times 10^{10}$	$2.85 \times 10^{10}$	$2.9 \times 10^{10}$
10	$1.19 \times 10^{10}$	$1.57 \times 10^{10}$		$2.3 \times 10^{10}$	$1.73 \times 10^{10}$	$1.89 \times 10^{10}$	$2.08 \times 10^{10}$	$2.12 \times 10^{10}$
FUSING FLUID TYPE (K) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (K) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4 *	Spec. 1	Spec. 2*	Spec. 3	Spec. 4
3	$4.4 \times 10^{10}$	$4.35 \times 10^{10}$	$3.9 \times 10^{10}$	$7.7 \times 10^8$	$3.25 \times 10^{10}$	$6.2 \times 10^8$	$1.7 \times 10^{10}$	$4.6 \times 10^{10}$
4	$2.95 \times 10^{10}$	$2.90 \times 10^{10}$	$2.7 \times 10^{10}$	$2.6 \times 10^9$	$1.48 \times 10^{10}$	$6.6 \times 10^8$	$14.4 \times 10^9$	$2.95 \times 10^{10}$
5	$2.2 \times 10^{10}$	$2.22 \times 10^{10}$	$2.06 \times 10^{10}$	$2.45 \times 10^9$	$1.68 \times 10^{10}$	$4.6 \times 10^8$	$1.24 \times 10^{10}$	$2.22 \times 10^{10}$
6	$1.7 \times 10^{10}$	$1.74 \times 10^{10}$	$1.65 \times 10^{10}$	$2.3 \times 10^9$	$1.49 \times 10^{10}$	$6.1 \times 10^8$	$1.05 \times 10^{10}$	$1.78 \times 10^{10}$
7	$1.44 \times 10^{10}$	$1.46 \times 10^{10}$	$1.39 \times 10^{10}$	$1.6 \times 10^9$	$1.32 \times 10^{10}$	$4.05 \times 10^8$	$9.1 \times 10^9$	$1.48 \times 10^{10}$
10	$1.06 \times 10^{10}$	$1.11 \times 10^{10}$	$1.05 \times 10^{10}$	$1.75 \times 10^9$	$10.1 \times 10^9$	$4.75 \times 10^8$	$7.75 \times 10^9$	$1.14 \times 10^{10}$

\* FAULTY SPECIMEN

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (J)  
72 Hr. Delay

CONFORMAL COATED  
0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID  
TYPE (J)  
72 Hr. Delay

CONFORMAL COATED  
100 VOLTS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#1	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$4.95 \times 10^7$	$7 \times 10^7$	$4.4 \times 10^7$	$3.6 \times 10^7$	$3.15 \times 10^{10}$	$1 \times 10^9$	$1.18 \times 10^9$	$1.2 \times 10^9$	$7.3 \times 10^8$
4	$1.2 \times 10^8$	$1.14 \times 10^8$	$9.7 \times 10^7$	$7.5 \times 10^7$	$2.85 \times 10^{10}$	$1.8 \times 10^9$	$1.94 \times 10^9$	$1.94 \times 10^9$	$1.14 \times 10^9$
5	$8.8 \times 10^7$	$1.36 \times 10^8$	$5.7 \times 10^7$	$7 \times 10^7$	$1.52 \times 10^{10}$	$8 \times 10^8$	$8.8 \times 10^8$	$8.6 \times 10^8$	$5.4 \times 10^8$
6	$1.08 \times 10^8$	$1.2 \times 10^8$	$9 \times 10^7$	$7.6 \times 10^7$	$1.76 \times 10^{10}$	$1.62 \times 10^9$	$1.65 \times 10^9$	$1.66 \times 10^9$	$1.07 \times 10^8$
7	$1.46 \times 10^8$	$1.48 \times 10^8$	$1.03 \times 10^8$	$1.06 \times 10^8$	$1.42 \times 10^{10}$	$1.52 \times 10^9$	$1.46 \times 10^9$	$1.48 \times 10^9$	$8.8 \times 10^8$
10	$2.2 \times 10^8$	$2.05 \times 10^8$	$2.2 \times 10^8$	$1.96 \times 10^8$	$1.28 \times 10^{10}$	$2.2 \times 10^9$	$2.15 \times 10^9$	$2.2 \times 10^9$	$1.32 \times 10^9$
FUSING FLUID TYPE (J) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (J) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#2	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$1.4 \times 10^{11}$	$3.15 \times 10^9$	$3.3 \times 10^8$	$4.15 \times 10^9$	$3.65 \times 10^{10}$	$5.6 \times 10^9$	$4.5 \times 10^9$	$3.6 \times 10^9$	
4	$1.94 \times 10^{11}$	$4.3 \times 10^9$	$1.2 \times 10^9$	$3.9 \times 10^9$	$2.75 \times 10^{10}$	$5.7 \times 10^9$	$4.8 \times 10^9$	$3.6 \times 10^9$	
5	$3.8 \times 10^{10}$	$2.85 \times 10^9$	$7.9 \times 10^8$	$2.85 \times 10^9$	$2 \times 10^{10}$	$4.2 \times 10^9$	$3.75 \times 10^9$	$2.9 \times 10^9$	
6	$9.6 \times 10^{10}$	$3.75 \times 10^9$	$1.2 \times 10^9$	$2.7 \times 10^9$	$1.84 \times 10^{10}$	$4.25 \times 10^9$	$3.8 \times 10^9$	$2.75 \times 10^9$	
7	$6 \times 10^{10}$	$2.75 \times 10^9$	$1.08 \times 10^9$	$2.4 \times 10^9$	$1.54 \times 10^{10}$	$3.75 \times 10^9$	$3.25 \times 10^9$	$2.35 \times 10^9$	
10	$1.38 \times 10^{11}$	$2.95 \times 10^9$	$1 \times 10^9$	$1.98 \times 10^9$	$1.2 \times 10^{10}$	$3.25 \times 10^9$	$2.3 \times 10^9$	$2 \times 10^9$	

NAC TR-2259

RAW DATA

FUSING FLUID

TYPE (L)

72 Hr. Delay

CONFORMAL COATED

0 VOLTS

Insulation Resistance - OHMS

FUSING FLUID

TYPE (L)

72 Hr. Delay

CONFORMAL COATED

100 VOLTS

Insulation Resistance - OHMS

DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#3	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$7.25 \times 10^7$	$6.0 \times 10^7$	$7.5 \times 10^7$	$6.4 \times 10^7$	$3.3 \times 10^9$	$4.5 \times 10^8$	$4.7 \times 10^8$	$9.2 \times 10^8$	$6.4 \times 10^8$
4	$8.9 \times 10^7$	$7.9 \times 10^7$	$9.6 \times 10^7$	$8.7 \times 10^7$	$3.3 \times 10^9$	$6.3 \times 10^8$	$6.5 \times 10^8$	$1.34 \times 10^9$	$9.4 \times 10^8$
5	$8.9 \times 10^7$	$6.8 \times 10^7$	$9.5 \times 10^7$	$9 \times 10^7$	$2.6 \times 10^9$	$5.2 \times 10^8$	$5.8 \times 10^8$	$1.06 \times 10^9$	$9.1 \times 10^8$
6	$1.02 \times 10^8$	$8.7 \times 10^7$	$1.06 \times 10^8$	$1.08 \times 10^8$	$3 \times 10^9$	$6.8 \times 10^8$	$7.5 \times 10^8$	$1.28 \times 10^9$	$1.12 \times 10^9$
7	$1.04 \times 10^8$	$9.4 \times 10^7$	$1.07 \times 10^8$	$1.14 \times 10^8$	$2.2 \times 10^9$	$7.2 \times 10^8$	$8.3 \times 10^8$	$1.26 \times 10^9$	$1.1 \times 10^9$
10	$1.18 \times 10^8$	$1.1 \times 10^8$	$1.06 \times 10^8$	$1.24 \times 10^8$	$2.15 \times 10^9$	$9.2 \times 10^8$	$9.5 \times 10^8$	$1.3 \times 10^9$	$1.22 \times 10^9$
FUSING FLUID TYPE (L) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (L) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
DAY	Spec. 1	Spec. 2	Spec. 3	Spec. 4		Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	$7.0 \times 10^9$	$8.85 \times 10^9$	$7.45 \times 10^9$	$7.6 \times 10^9$		$10.0 \times 10^9$	$1.14 \times 10^{10}$	$1.16 \times 10^{10}$	$9.6 \times 10^9$
4	$5.9 \times 10^9$	$7.5 \times 10^9$	$7 \times 10^9$	$7.1 \times 10^9$		$8.6 \times 10^9$	$1.04 \times 10^{10}$	$1.02 \times 10^{10}$	$8 \times 10^9$
5	$4.5 \times 10^9$	$5.8 \times 10^9$	$5.7 \times 10^9$	$5.9 \times 10^9$		$6.4 \times 10^9$	$8.1 \times 10^9$	$8.5 \times 10^9$	$6.5 \times 10^9$
6	$4.05 \times 10^9$	$5 \times 10^9$	$5.1 \times 10^9$	$5.1 \times 10^9$		$5.8 \times 10^9$	$7 \times 10^9$	$7.6 \times 10^9$	$5.8 \times 10^9$
7	$3.5 \times 10^9$	$4.4 \times 10^9$	$4.35 \times 10^9$	$4.7 \times 10^9$		$5.05 \times 10^9$	$6.2 \times 10^9$	$6.8 \times 10^9$	$4.95 \times 10^9$
10	$2.7 \times 10^9$	$3.45 \times 10^9$	$3.45 \times 10^9$	$3.65 \times 10^9$		$4.7 \times 10^9$	$4.9 \times 10^9$	$5.8 \times 10^9$	$3.75 \times 10^9$

NAC TR-2259  
RAW DATA

DAY	FUSING FLUID TYPE (0) 72 Hr. Delay CONFORMAL COATED 0 VOLTS Insulation Resistance - OHMS				FUSING FLUID TYPE (0) 72 Hr. Delay CONFORMAL COATED 100 VOLTS Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	1.26x10 <sup>8</sup>	1.46x10 <sup>8</sup>	1.08x10 <sup>9</sup>	5.8x10 <sup>8</sup>	9.0x10 <sup>7</sup>	2.57x10 <sup>8</sup>	8.2x10 <sup>8</sup>	1.2x10 <sup>9</sup>
4	1.69x10 <sup>8</sup>	1.84x10 <sup>8</sup>	1.2x10 <sup>9</sup>	6.8x10 <sup>8</sup>	1x10 <sup>8</sup>	3x10 <sup>8</sup>	9.4x10 <sup>8</sup>	1.27x10 <sup>9</sup>
5	1.78x10 <sup>8</sup>	1.94x10 <sup>8</sup>	1.09x10 <sup>9</sup>	6.8x10 <sup>8</sup>	1.02x10 <sup>8</sup>	2.85x10 <sup>8</sup>	8.3x10 <sup>8</sup>	1.18x10 <sup>9</sup>
6	2.1x10 <sup>8</sup>	2.25x10 <sup>8</sup>	1.08x10 <sup>9</sup>	7.6x10 <sup>8</sup>	1.12x10 <sup>8</sup>	3.05x10 <sup>8</sup>	9.3x10 <sup>8</sup>	1.22x10 <sup>9</sup>
7	2.25x10 <sup>8</sup>	2.4x10 <sup>8</sup>	1.02x10 <sup>9</sup>	7.5x10 <sup>8</sup>	1.12x10 <sup>8</sup>	3.05x10 <sup>8</sup>	9.1x10 <sup>8</sup>	1.16x10 <sup>9</sup>
10	2.15x10 <sup>8</sup>	2.35x10 <sup>8</sup>	8.9x10 <sup>8</sup>	7x10 <sup>8</sup>	1.2x10 <sup>8</sup>	3.05x10 <sup>8</sup>	8.7x10 <sup>8</sup>	1.16x10 <sup>9</sup>
	FUSING FLUID TYPE (0) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS				FUSING FLUID TYPE (0) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	6.6x10 <sup>8</sup>	1.18x10 <sup>9</sup>	8.0x10 <sup>8</sup>	3.05x10 <sup>8</sup>	8.5x10 <sup>8</sup>	5.7x10 <sup>8</sup>	1.09x10 <sup>9</sup>	2.03x10 <sup>9</sup>
4	5.6x10 <sup>8</sup>	1.02x10 <sup>9</sup>	8.1x10 <sup>8</sup>	3.25x10 <sup>8</sup>	8.3x10 <sup>8</sup>	5.6x10 <sup>8</sup>	1.07x10 <sup>9</sup>	1.9x10 <sup>9</sup>
5	5.4x10 <sup>8</sup>	8.9x10 <sup>8</sup>	7.5x10 <sup>8</sup>	3.2x10 <sup>8</sup>	7.7x10 <sup>8</sup>	5.5x10 <sup>8</sup>	1.07x10 <sup>8</sup>	1.68x10 <sup>9</sup>
6	4.95x10 <sup>8</sup>	8.0x10 <sup>8</sup>	7.1x10 <sup>8</sup>	3.25x10 <sup>8</sup>	7.5x10 <sup>8</sup>	5.6x10 <sup>8</sup>	9.9x10 <sup>8</sup>	1.58x10 <sup>9</sup>
7	4.55x10 <sup>8</sup>	7.1x10 <sup>8</sup>	6.4x10 <sup>8</sup>	3.15x10 <sup>8</sup>	7.3x10 <sup>8</sup>	5.6x10 <sup>8</sup>	9.5x10 <sup>8</sup>	1.46x10 <sup>9</sup>
10	4.25x10 <sup>8</sup>	6.2x10 <sup>8</sup>	5.6x10 <sup>8</sup>	3x10 <sup>8</sup>	6.9x10 <sup>8</sup>	5.5x10 <sup>8</sup>	8.9x10 <sup>8</sup>	1.34x10 <sup>9</sup>

NAC TR-2259  
RAW DATA

FUSING FLUID  
TYPE (M)  
72 Hr. Delay  
CONFORMAL COATED  
0 VOLTS

FUSING FLUID  
TYPE (M)  
72 Hr. Delay  
CONFORMAL COATED  
100 VOLTS

DAY	Insulation Resistance - OHMS					Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#1	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	12x10 <sup>9</sup>	9x10 <sup>9</sup>	1.9x10 <sup>10</sup>	1.8x10 <sup>10</sup>	15x10 <sup>9</sup>	16x10 <sup>9</sup>	16x10 <sup>9</sup>	4.6x10 <sup>9</sup>	12x10 <sup>9</sup>
4	10.8x10 <sup>9</sup>	7.9x10 <sup>9</sup>	13.4x10 <sup>9</sup>	14x10 <sup>9</sup>	10x10 <sup>9</sup>	12.3x10 <sup>9</sup>	12.2x10 <sup>9</sup>	4.5x10 <sup>9</sup>	10.1x10 <sup>9</sup>
5	8.2x10 <sup>9</sup>	7.1x10 <sup>9</sup>	1.22x10 <sup>10</sup>	1.24x10 <sup>10</sup>	8.1x10 <sup>9</sup>	1.15x10 <sup>10</sup>	1.07x10 <sup>10</sup>	4.1x10 <sup>9</sup>	8.15x10 <sup>9</sup>
6	5.8x10 <sup>9</sup>	5.3x10 <sup>9</sup>	9.0x10 <sup>9</sup>	9.2x10 <sup>9</sup>	5.5x10 <sup>9</sup>	8.2x10 <sup>9</sup>	8.5x10 <sup>9</sup>	3.2x10 <sup>9</sup>	6.9x10 <sup>9</sup>
7	4.9x10 <sup>9</sup>	5.1x10 <sup>9</sup>	8.5x10 <sup>9</sup>	8.5x10 <sup>9</sup>	5.1x10 <sup>9</sup>	7.4x10 <sup>9</sup>	8x10 <sup>9</sup>	3.3x10 <sup>9</sup>	6.5x10 <sup>9</sup>
10	3.8x10 <sup>9</sup>	4.5x10 <sup>9</sup>	6.8x10 <sup>9</sup>	7.0x10 <sup>9</sup>	4.7x10 <sup>9</sup>	7.1x10 <sup>9</sup>	7.3x10 <sup>9</sup>	3.2x10 <sup>9</sup>	5.8x10 <sup>9</sup>
<p>FUSING FLUID TYPE (M) 72 Hr. Delay SOLDER MASK 0 VOLTS</p>					<p>FUSING FLUID TYPE (M) 72 Hr. Delay SOLDER MASK 100 VOLTS</p>				
	Insulation Resistance - OHMS					Insulation Resistance - OHMS			
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Control#2	Spec. 1	Spec. 2	Spec. 3	Spec. 4
3	12x10 <sup>9</sup>	5.8x10 <sup>9</sup>	9x10 <sup>9</sup>	8.5x10 <sup>9</sup>	9x10 <sup>9</sup>	9x10 <sup>9</sup>	7x10 <sup>9</sup>	8.5x10 <sup>9</sup>	8.5x10 <sup>9</sup>
4	8x10 <sup>9</sup>	4.7x10 <sup>9</sup>	7.9x10 <sup>9</sup>	7.2x10 <sup>9</sup>	5.5x10 <sup>9</sup>	7.7x10 <sup>9</sup>		8x10 <sup>9</sup>	7.3x10 <sup>9</sup>
5	8x10 <sup>9</sup>	4x10 <sup>9</sup>	6.45x10 <sup>9</sup>	5.9x10 <sup>9</sup>	4.6x10 <sup>9</sup>	6.45x10 <sup>9</sup>	6.1x10 <sup>9</sup>	7x10 <sup>9</sup>	6x10 <sup>9</sup>
6	5.9x10 <sup>9</sup>	3.5x10 <sup>9</sup>	5.6x10 <sup>9</sup>	5.3x10 <sup>9</sup>	3.4x10 <sup>9</sup>	5.5x10 <sup>9</sup>	4.9x10 <sup>9</sup>	5.8x10 <sup>9</sup>	5.2x10 <sup>9</sup>
7	2.6x10 <sup>9</sup>	3.2x10 <sup>9</sup>	5.9x10 <sup>9</sup>	5.1x10 <sup>9</sup>	2.9x10 <sup>9</sup>	5.5x10 <sup>9</sup>	4.9x10 <sup>9</sup>	5.5x10 <sup>9</sup>	4.3x10 <sup>9</sup>
10	2.2x10 <sup>9</sup>	2.9x10 <sup>9</sup>	4.1x10 <sup>9</sup>	3.5x10 <sup>9</sup>	2.2x10 <sup>9</sup>	4.6x10 <sup>9</sup>	4.3x10 <sup>9</sup>	4.9x10 <sup>9</sup>	4.7x10 <sup>9</sup>

NAC TR-2259  
RAW DATA

DAY	FUSING FLUID TYPE (N) 72 Hr. Delay CONFORMAL COATED 0 VOLTS Insulation Resistance - OHMS				FUSING FLUID TYPE (N) 72 Hr. Delay CONFORMAL COATED 100 VOLTS Insulation Resistance - OHMS				
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4	
3	2.4x10 <sup>7</sup>	* 2.8x10 <sup>10</sup>	6.5x10 <sup>6</sup>	12.3x10 <sup>6</sup>	2.8x10 <sup>8</sup>	1.6x10 <sup>8</sup>	13x10 <sup>7</sup>	13.5x10 <sup>7</sup>	
4	* 7.5x10 <sup>11</sup>	9x10 <sup>6</sup>	* 3.7x10 <sup>10</sup>	2.3x10 <sup>7</sup>	* 7.2x10 <sup>12</sup>	* 17.5x10 <sup>12</sup>	2.3x10 <sup>8</sup>	2.1x10 <sup>8</sup>	
5	1.44x10 <sup>7</sup>	2.75x10 <sup>7</sup>	12x10 <sup>6</sup>	4.25x10 <sup>7</sup>	2.8x10 <sup>8</sup>	3.15x10 <sup>8</sup>	3.25x10 <sup>8</sup>	2.75x10 <sup>8</sup>	
6	3.3x10 <sup>7</sup>	5.8x10 <sup>7</sup>	2.4x10 <sup>7</sup>	4.3x10 <sup>7</sup>	2.5x10 <sup>8</sup>	3.2x10 <sup>8</sup>	2.8x10 <sup>8</sup>	2.8x10 <sup>8</sup>	
7	3.5x10 <sup>7</sup>	5.8x10 <sup>7</sup>	4x10 <sup>7</sup>	7.2x10 <sup>7</sup>	2.9x10 <sup>8</sup>	3.4x10 <sup>8</sup>	3.4x10 <sup>8</sup>	3.1x10 <sup>8</sup>	
10	4.0x10 <sup>7</sup>	7.5x10 <sup>7</sup>	5.5x10 <sup>7</sup>	9.0x10 <sup>7</sup>	3.7x10 <sup>8</sup>	4.5x10 <sup>8</sup>	5.3x10 <sup>8</sup>	4.3x10 <sup>8</sup>	
* Operator Error									
FUSING FLUID TYPE (N) 72 Hr. Delay SOLDER MASK 0 VOLTS Insulation Resistance - OHMS					FUSING FLUID TYPE (N) 72 Hr. Delay SOLDER MASK 100 VOLTS Insulation Resistance - OHMS				
	Spec. 1	Spec. 2	Spec. 3	Spec. 4	Spec. 1	Spec. 2	Spec. 3	Spec. 4	
3	5.5x10 <sup>9</sup>	5.5x10 <sup>9</sup>	3.7x10 <sup>9</sup>	5.2x10 <sup>9</sup>	3.1x10 <sup>9</sup>	2.7x10 <sup>9</sup>	2.8x10 <sup>9</sup>	2.7x10 <sup>9</sup>	
4	4.7x10 <sup>9</sup>	4x10 <sup>9</sup>	3.1x10 <sup>9</sup>	* 5.2x10 <sup>12</sup>	2.6x10 <sup>9</sup>	2.2x10 <sup>9</sup>	* 3x10 <sup>11</sup>	2.2x10 <sup>9</sup>	
5	3.8x10 <sup>9</sup>	3.2x10 <sup>9</sup>	3x10 <sup>9</sup>	3.45x10 <sup>9</sup>	2.15x10 <sup>9</sup>	1.98x10 <sup>9</sup>	2x10 <sup>9</sup>	1.63x10 <sup>9</sup>	
6	3.1x10 <sup>9</sup>	2.6x10 <sup>9</sup>	2.4x10 <sup>9</sup>	2.7x10 <sup>9</sup>	1.8x10 <sup>9</sup>	1.9x10 <sup>9</sup>	1.7x10 <sup>9</sup>	1.6x10 <sup>9</sup>	
7	3.1x10 <sup>9</sup>	2.4x10 <sup>9</sup>	2x10 <sup>9</sup>	2.4x10 <sup>9</sup>	1.6x10 <sup>9</sup>	1.5x10 <sup>9</sup>	1.6x10 <sup>9</sup>	1.4x10 <sup>9</sup>	
10	2.1x10 <sup>9</sup>	1.7x10 <sup>9</sup>	1.6x10 <sup>9</sup>	1.8x10 <sup>9</sup>	1.3x10 <sup>9</sup>	1.3x10 <sup>9</sup>	1.3x10 <sup>9</sup>	1.2x10 <sup>9</sup>	

\* Operator Error

TABLE V  
 FORMULA FOR LINEAR REGRESSION LINES OF RESISTANCE VS TIME AND ANALYSIS OF LINE SLOPES  
 72 HOUR DELAY BEFORE FUSING FLUID REMOVAL ("A", "B", AND "C" FUSING FLUIDS)

CONDITIONS	"A" FUSING FLUID	"B" FUSING FLUID	"C" FUSING FLUID
0 Volts Electrical Stress, Conformally Coated	$\log R = .0425T + .571$	$\log R = .00735T + .456$	$\log R = -.0418T + .679$
100 Volts Electrical Stress, Conformally Coated	$\log R = .563T - .119$	$\log R = .0293T + .5968$	$\log R = -.0316T + 1.25$
0 Volts Electrical Stress, Solder Mask Coated	$\log R = -.038T + 1.625$	$\log R = -.00383T + .3125$	$\log R = -.0556T + .453$
100 Volts Electrical Stress, Solder Mask Coated	$\log R = -.01133T + .388$	$\log R = .0127T + .381$	$\log R = -.038T + .958$
$\bar{X}$ Slopes	.1178	.005205	-.04175
$\sigma$ Slopes	.2573	.01551	.00879
$\bar{X} + 3\sigma$	.8897	.05175	-.01538
$\bar{X} - 3\sigma$	-.6542	-.04134	-.06811
Trend of Slopes Is	Positive	Positive	Negative

TABLE VI  
 FORMULA FOR LINEAR REGRESSION LINES OF RESISTANCE VS TIME AND ANALYSIS OF LINE SLOPES  
 168 HOUR DELAY BEFORE FUSING FLUID REMOVAL ("A", "B", AND "C" FUSING FLUIDS)

CONDITIONS	"A" FUSING FLUID	"B" FUSING FLUID	"C" FUSING FLUID
0 Volts Electrical Stress, Conformally Coated	$\log R = .0296T + .3103$	$\log R = .0357T + .26$	$\log R = -.043T + .75$
100 Volts Electrical Stress, Conformally Coated	$\log R = .0079T + .859$	$\log R = .0255T + .472$	$\log R = -.027T + .673$
0 Volts Electrical Stress, Solder Mask Coated	$\log R = -.145T + 1.38$	$\log R = -.1044T + 1.18$	$\log R = -.147T + 1.04$
100 Volts Electrical Stress, Solder Mask Coated	$\log R = -.122T + 2.05$	$\log R = -.0868T + 1.07$	$\log R = -.137T + 1.612$
$\bar{X}$ Slopes	-.05738	-.0325	-.08850
$\sigma$ Slopes	.07694	.06351	.05391
$\bar{X} + 3\sigma$	.1734	.1580	.07324
$\bar{X} - 3\sigma$	-.2882	-.2230	-.2502
Trend of Slopes Is	Negative	Negative	Negative

TABLE VII  
 FORMULA FOR LINEAR REGRESSION LINES OF RESISTANCE VS TIME AND ANALYSIS OF LINE SLOPES  
 72 HOUR DELAY BEFORE FUSING FLUID REMOVAL ("F", "I", AND "K" FUSING FLUIDS)

CONDITIONS	"F" FUSING FLUID	"I" FUSING FLUID	"K" FUSING FLUID
0 Volts Electrical Stress, Conformally Coated	$\log R = -.0919T+.988$	$\log R = -.0948T+.777$	$\log R = -.0747T+.884$
100 Volts Electrical Stress, Conformally Coated	$\log R = -.0857T+.905$	$\log R = -.0843T+.784$	$\log R = -.101T+1.206$
0 Volts Electrical Stress, Solder Mask Coated	$\log R = -.103T+.902$	$\log R = -.0804T+.531$	$\log R = -.0822T+.781$
100 Volts Electrical Stress, Solder Mask Coated	$\log R = -.0768T+.714$	$\log R = -.0697T+.662$	$\log R = -.0631T+.563$
$\bar{X}$ Slopes	-.0894	-.0823	-.0803
$\sigma$ Slopes	.00953	.00898	.0138
$\bar{X} + 3\sigma$	-.0607	-.0554	-.0389
$\bar{X} - 3\sigma$	-.118	-.109	-.122
Trend of Slopes Is	Negative	Negative	Negative

TABLE VIII  
 FORMULA FOR LINEAR REGRESSION LINES OF RESISTANCE VS TIME AND ANALYSIS OF LINE SLOPES  
 72 HOUR DELAY BEFORE FUSING FLUID REMOVAL ("J", "L", AND "O" FUSING FLUID)

CONDITIONS	log R =	log R =	log R =
0 Volts Electrical Stress, Conformally Coated	.0782T-.455	.0296T-.209	.0133T+.5299
100 Volts Electrical Stress, Conformally Coated	.0321T-.117	.0555T+.559	.00572T+.595
0 Volts Electrical Stress, Solder Mask Coated	-.00618T+.759	-.0538T+1.03	-.0232T+.883
100 Volts Electrical Stress, Solder Mask Coated	-.0402T+.784	-.0508T+1.146	-.00698T+.962
$\bar{X}$ Slopes	.0160	-.00513	-.00279
$\sigma$ Slopes	.0441	.0482	.0138
$\bar{X} + 3\sigma$	.148	.139	.0387
$\bar{X} - 3\sigma$	-.1163	-.150	-.0443
Trend of Slopes Is	Positive	Negative	Negative

TABLE IX

FORMULA FOR LINEAR REGRESSION LINES OF RESISTANCE VS TIME AND ANALYSIS OF LINE SLOPES  
 72 HOUR DELAY BEFORE FUSING FLUID REMOVAL ("M" AND "N" FUSING FLUIDS)

CONDITIONS	"M" FUSING FLUID	"N" FUSING FLUID
0 Volts Electrical Stress, Conformally Coated	$\log R = -.0603T+1.281$	$\log R = .0758T+.0649$
100 Volts Electrical Stress, Conformally Coated	$\log R = -.0423T+1.116$	$\log R = .055T+.119$
0 Volts Electrical Stress, Solder Mask Coated	$\log R = -.0632T+1.089$	$\log R = -.0616T+.838$
100 Volts Electrical Stress, Solder Mask Coated	$\log R = -.0376T+1.00$	$\log R = -.0484T+.554$
$\bar{X}$ Slopes	-.0509	.0052
$\sigma$ Slopes	.0111	.0608
$\bar{X} + 3\sigma$	-.0176	.188
$\bar{X} - 3\sigma$	-.0841	-.177
Trend of Slopes Is	Negative	Positive


NAC TR-2259

TABLE X

MIL-P-28809 IONIC CONTAMINANTS TEST

CLEANING DELAY	RESISTIVITY OHM-CM x 10 <sup>e</sup>	RESISTIVITY OHM-CM x 10 <sup>e</sup>	RESISTIVITY OHM-CM x 10 <sup>e</sup>	BEGINNING RESISTIVITY OF WASH SOLUTION OHM-CM x 10 <sup>e</sup>
	"A" FUSING FLUID	"B" FUSING FLUID	"C" FUSING FLUID	
72 Hour Specimen 1	9.4	9.8	24.6	57.0
Specimen 2	8.0	10.8	30	
Specimen 3	8.5	9.8	30	
168 Hour Specimen 1	3.4	4.6	10.3	24.0
Specimen 2	3.1	3.3	9.1	
Specimen 3	3.1	6.0	12.0	
	"F" FUSING FLUID	"I" FUSING FLUID	"K" FUSING FLUID	
72 Hour Specimen 1	7.2	17.4	20.0	20.0
Specimen 2	7.0	17.5	21.0	
Specimen 3	6.6	17.4	19.0	
	"J" FUSING FLUID	"L" FUSING FLUID	"O" FUSING FLUID	
72 Hour Specimen 1	2.5	4.9	4.5	> 25.0
Specimen 2	2.0	5.5	3.2	
Specimen 3	3.4	5.4	5.0	
	"M" FUSING FLUID	"N" FUSING FLUID		
72 Hour Specimen 1	15.0	- - -		27.0
Specimen 2	14.8	5.4		
Specimen 3	13.5	4.7		

EQUILIBRATION OF COMB  
PATTERN TO MIL-P-55110  
TRUMPET PATTERN

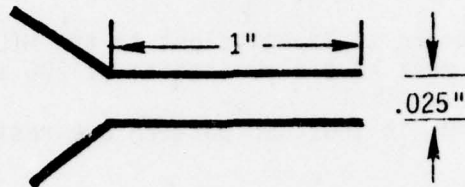

MIL-P-55110 TRUMPET PATTERN

1. Number of resistance squares

$$\frac{1.00''}{.025''} = 40 \text{ squares}$$

2. Assume the squares are resistors connected in parallel

$$\frac{1}{R_T} = \frac{1}{R_1} + \frac{1}{R_2} + \dots + \frac{1}{R_{40}}$$

$$\frac{1}{R_T} = \frac{40}{R_S}$$

Where  $R_T = 500 \times 10^6$  ohms per MIL-P-55110


$R_S$  = resistance of each square.

3.  $R_T = \frac{R_S}{40}$

4.  $500 \times 10^6 = \frac{R_S}{40}$

$$R_S = 200 \times 10^8 \text{ ohms}$$

Resistance measured portion  
of comb pattern specimen

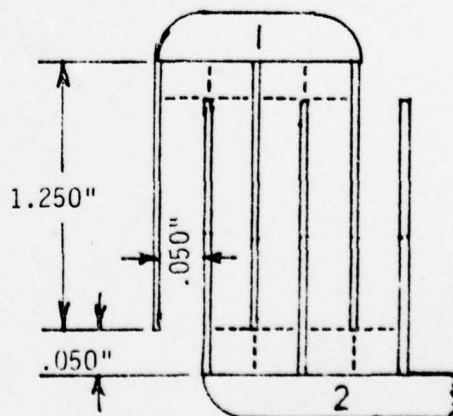

5. Number of resistance squares

$$\frac{1.250'' - .050''}{.050''} \times 5 + 8 \text{ corner squares at the ends of the conductors} = 128 \text{ squares.}$$

6. For this comb pattern to be equivalent to the MIL-P-55110 trumpet pattern, each square must have a resistance of  $200 \times 10^8$  ohms.

7. Assumes the squares in the comb pattern are resistors in parallel

$$\frac{1}{R_T} = \frac{1}{R_1} + \frac{1}{R_2} + \dots + \frac{1}{R_{128}}$$

$$\frac{1}{R_T} = \frac{128}{R_S}$$

where

$$R_T = \text{total resistance}$$

$$R_S = 200 \times 10^8 \text{ ohms}$$

8. 
$$R_T = \frac{R_S}{128}$$

9. 
$$R_T = \frac{200 \times 10^8}{128}$$

$$R_T \approx 1.5 \times 10^8 \text{ ohms}$$

10. Therefore, the comb pattern specimen has a MIL-P-55110 equivalent value of  $1.5 \times 10^8$  ohms. Any resistance value less than this during testing was a failure.

## MATERIALS

1. Circuit Board Material  
FL-GF, .062, C1/1
2. Solder Mask  
Photocircuits Co.  
PC-401  
Epoxy type
3. Conformal Coating  
Conap, Inc.  
CE-1155  
Polyurethane type
4. Electrical Leads  
200AS100-18 wire
5. Wire Solder  
WRP-2
6. Fusing Fluids  
The identity of the fusing fluids is available only to the funding source of this study because of their proprietary nature.

EQUIPMENT

1. Temperature and Humidity Chamber  
Blue M Co.  
Model FR-256BP
2. Power Supply  
Lambda Co.  
Model LP-534-FM
3. Megohm Bridge  
General Radio Co.  
Model 1644-A
4. Vapor Cleaner  
Acra Electric Corp.  
Spee Degreaser Model D-3
5. Infra-Red Solder Fusing Machine  
Research, Inc.  
Model 4384
6. MIL-P-28809 Apparatus as described  
in Naval Avionics Center Materials  
Research Report 3-78.



APPLICATION		REVISIONS			
NEXT ASSY	USED ON	LTR	DESCRIPTION	DATE	APPROVED



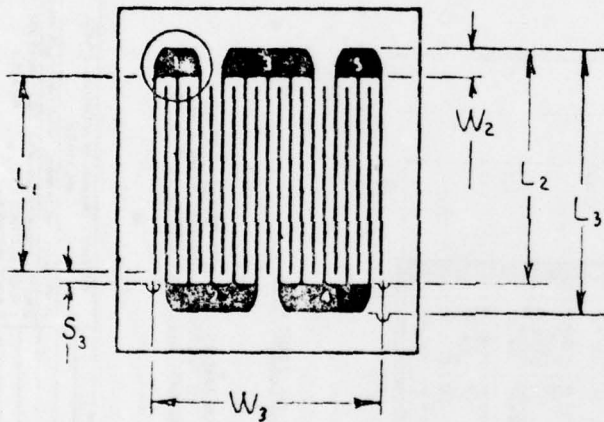


TABLE		
CODE	DIM.	TOL.
$L_1$	1.250	+ .000 - .004
$L_2$	1.550	+ .000 - .004
$L_3$	1.750	+ .000 - .004
$S_1$	.050	+ .004 - .000
$S_2$	.050	+ .004 - .000
$S_3$	.050	+ .004 - .000
$W_1$	.025	+ .000 - .004
$W_2$	.200	+ .000 - .004
$W_3$	1.525	+ .000 - .004

REV STATUS	REV																					
OF SHEETS	SHEET	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21
INTERPRET DRAWING IN ACCORDANCE WITH MIL-STD-100		NAVAL AVIONICS FACILITY INDIANAPOLIS, IND. 46218										DEPARTMENT OF THE NAVY NAVAL SYSTEMS COMMAND WASHINGTON, D. C. 20360										
DIMENSIONS ARE IN INCHES		UNLESS OTHERWISE SPECIFIED, TOLERANCES ARE: 3 PLACE DECIMALS ± 2 PLACE DECIMALS ± ANGLES ±		PROJ ENGR <i>H. T. Holson</i> 5-12-78		COMB SPECIMEN																
		ENGINEER		CHECKED												PREPARED <i>J. L. Wash</i> 4-06-78						
MATERIAL ENGR		APPROVED FOR THE COMMAND										SIZE A		CODE IDENT NO.		DRAWING NO. AV-22107						
CIRCUIT ENGR												SCALE 1 : 1		SHEET 1 OF 1								

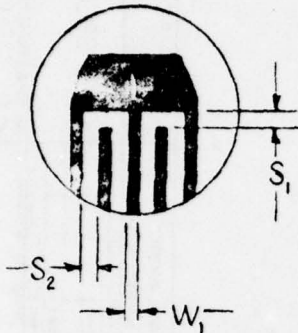




NOTES:  
 1- THIS PRODUCTION MASTER HAS BEEN DECLARED FOR FABRICATION BY THE SUBTRACTIVE PROCESS, FROM BASE MATERIAL CLAD WITH 1oz / SQ FT COPPER FOR

INDEX HOLE LOCATIONS	
AXIS	COORDINATES
A	0.000
B	3.000
C	5.000
D	7.000
E	9.000
F	11.000
1	0.250
2	3.250
3	6.250
4	9.250
5	12.250

REVISION NO. OF SHEET	REVISED BY	DATE	APPROVED
1			
DESCRIPTION		DATE	APPROVED
COMB SPECIMEN (AV22109)			
DEPARTMENT OF THE NAVY		WASHINGTON, D. C.	
NAVAL AVIONICS FACILITY		MEMPHIS, TN 38218	
INTERPRET DRAWING, IN ACCORDANCE WITH MIL STD 1001		DO NOT SCALE THIS DRAWING. DIMENSIONS ARE IN INCHES.	
UNLESS OTHERWISE SPECIFIED, TOLERANCES ARE 3 PLACE DECIMALS.		2 PLACE DECIMALS.	
REMOVE BURRS. BREAK SHARP EDGES.		MATERIAL COVER: GAL. BRASS (15% ZINC)	
MIL-P-13940, PL-GF-062-G-7-R18		SCALE: 1" = 1"	
NET ASST. USED ON APPLICATION		SHEET NO. 19	
		AV 22109	

BARNSTEAD HOSE NIPPLE  
 CARTRIDGE D 8902 ULTRA-PURE  
 (MIXED BED) MAXIMUM FLOW RATE  
 PER CARTRIDGE 12 GALLONS PER HOUR.

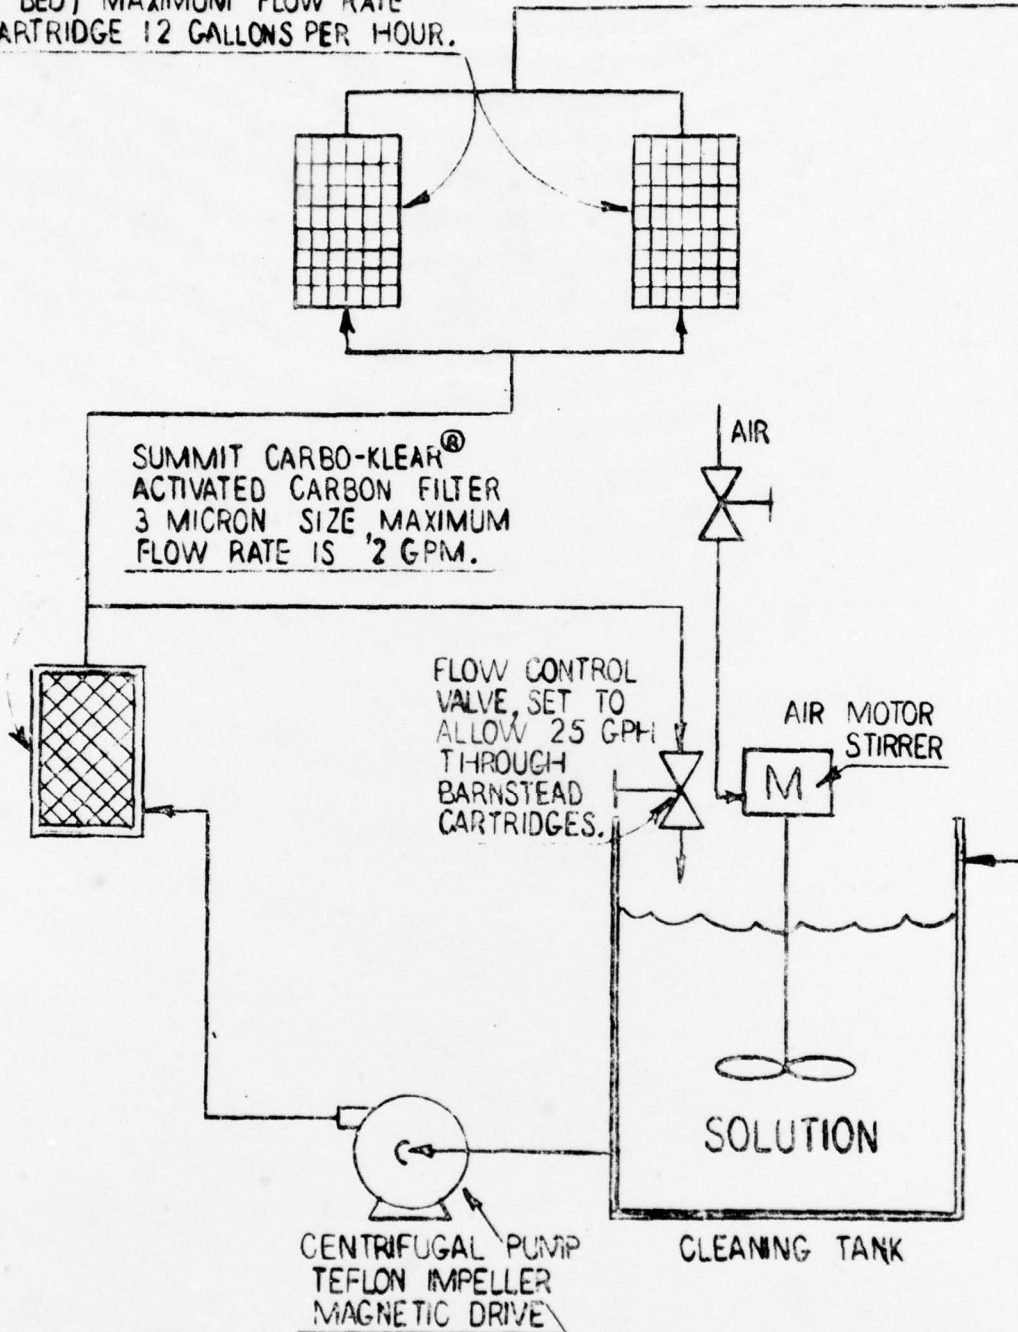

SYSTEM SOLUTION

75% 2-PROPANOL  
 25% DEIONIZED WATER  
 APPROXIMATELY 12 GALLONS

Page A-28

DRAWN BY <i>J. Washon</i>		CLEANING SYSTEM SCHEMATIC	
PROJ. ENGR. <i>R.E. Martz</i>	SIZE A	CODE IDENT NO. 02387	DRAWING NO. AV 21922
DATE 8-2-77	SCALE ~	REV	SHEET 1 of 1

NAC TR-2259

DISTRIBUTION

COPIES

Commander Naval Air Systems Command Department of the Navy Washington, DC 20361 AIR-533F AIR-533FL	1 1
Commanding Officer Naval Electronics Systems Command Washington, DC 20360 50452 (J. Kerr)	1
Commander Naval Weapons Center China Lake, CA 93555 3681 (J. Rabe)	1
Commanding Officer Naval Air Engineering Center Lakehurst, NJ 08733 ESSD 9313 (D. Broude)	1
Commanding Officer Rome Air Development Center Griffiss Air Force Base, NY 13441 RBRM (J. McCormick)	3
Director Air Force Systems Command Wright-Patterson Air Force Base, OH 45433 ASD/ENESS (R. Faust) AFML/LTE (D. Knapke)	1 1
Director Air Force Rocket Propulsion Laboratory Edwards Air Force Base, CA 93523 DOS (T.Sgt. D. Freundner)	1
Director Space and Missile Systems Organization P.O. Box 92960, World Wide Postal Center Los Angeles, CA 90009	1

NAC TR-2259

Hollis Engineering, Inc. P. O. Box 1189 15 Charron Ave. Nashua, NH 03061 Attn: Ken Boynton, Exec. Vice Pres.	1
Electrovert, Inc. 86 Hartford Ave. Mt. Vernon, NY 10553 Attn: Paul J. Bud, Technical Director	1
E. I. DuPont Corp. Freon Products Laboratory Wilmington, DE 19898 Attn: William G. Kenyon	1
Alpha Metals, Inc. 56 Water Street Jersey City, NJ 07304 Attn: James P. Langan, National Prod. Mgr.	1
Kenco Alloy & Chemical Co., Inc. 418 West Belden Avenue Addison, IL 60101 Attn: Kenneth J. Barry, President	1
DDC	10
265	1
410	1
415	1
423	1
443	1
700	1
710	2
712	1
713	1
714	3
900	1

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.  
This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.  
This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.  
This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.  
This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.

This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.

This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.

This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

Naval Avionics Center (NAC Report  
TR-2259)

Deleterious Effect of Fusing Fluids  
on Printed Wiring Boards, by David O.  
Pond, 9 May 1979

UNCLASSIFIED, 56 p.

This study identified the corrosive  
effects of fusing fluids and fusing  
fluid residues on printed wiring  
boards subjected to electrical stress  
in a humid environment at elevated  
temperature. The effect of varying  
delay times between solder fusing and  
cleaning of fusing fluid residues for  
three fusing fluids was studied. The

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED

effect of a single delay time between solder fusing and cleaning of fusing fluid residues for eight other fusing fluids was studied. Also, the protective value of a solder resist and a conformal coating was evaluated.

UNCLASSIFIED