

AD-A075 342

TECHNICAL LIBRARY

AD

MEMORANDUM REPORT ARLCB-MR-79013

A SHORT STUDY OF LARGE ROTARY FORGED CYLINDERS

F. Heiser

June 1979



US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND
LARGE CALIBER WEAPON SYSTEMS LABORATORY
BENÉT WEAPONS LABORATORY
WATERVLIET, N. Y. 12189

AMCMS No. 612603H181011

DA Project No. 1L1626603AH18

PRON No. 1A924362GGGG

DTIC QUALITY INSPECTED 3

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

DISPOSITION

Destroy this report when it is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER ARLCB-MR-79013	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) A SHORT STUDY OF LARGE ROTARY FORGED CYLINDERS		5. TYPE OF REPORT & PERIOD COVERED
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) F. Heiser		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Benet Weapons Laboratory Watervliet Arsenal, Watervliet, N.Y. 12189 DRDAR-LCB-TL		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AMCMS No. 612603H181011 DA Proj No. 1L1626603AH18 PRON No. 1A924362GGGG
11. CONTROLLING OFFICE NAME AND ADDRESS US Army Armament Research and Development Command Large Caliber Weapon Systems Laboratory Dover, New Jersey 07801		12. REPORT DATE June 1979
		13. NUMBER OF PAGES 35
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) ESR Steel Hollow ESR Steel Rotary Forge Vacuum Degassed Steel		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The Integrated Forging Line was used to produce steel for the Advanced Breech Technology program. Cylinders were rotary forged from cast hollow ESR and from vacuum degassed steel. Anomalies in the data prompted a more detailed metallurgical study. The results are presented. Satisfactory properties were produced from the vacuum degassed steel. However, the very light forging reduction coupled with the very rapid and short austenitizing inherent in the Selas heat treatment system were inadequate to develop satisfactory properties		

Continued from Block 20
in the cast ESR steel.

TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION	1
PRODUCTION OF FULL-SIZE CYLINDERS	1
Hollow ESR Ingot	1
Forged Vacuum Degassed Preform	4
Additional Work - Hollow ESR Ingot	5
DISCUSSION AND CONCLUSIONS	8

TABLES

Table

1	Hollow ESR Processing History	10
2,3	Hollow ESR Rotary Forged Selas Heat Treat	12,13
4	Vacuum Degassed Processing History	14
5	Vacuum Degassed (Forged) Rotary Forged Selas Heat Treat	15
6	Vacuum Degassed (Forged) Rotary Forged Selas Heat Treat Retemper - Standard Furnace	16
7	Hollow ESR Rotary Forged Selas Heat Treat Reheat Treated in Small Sections	17
8	Hollow ESR Rotary Forged Selas Heat Treat Reheat Treated in Full Wall Thickness Sections	18

ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	Microstructure at mid-wall of heat treated rotary forged hollow ESR cylinder (Top)	19
2	Microstructure at mid-wall of heat treated rotary forged hollow ESR cylinder (Bottom)	20
3	Microstructure of heat treated rotary forged hollow ESR cylinder (Top)	21
4	Microstructure at mid-wall of reheat treated rotary forged hollow ESR cylinder (Top)	22
5	Microstructure of heat treated rotary forged vacuum degassed cylinder (Top)	23
6	Microstructure at mid-wall of reheat treated rotary forged vacuum degassed cylinder (Bottom)	24
7	Microstructure at mid-wall of reheat treated rotary forged cylinders - Martensite-Bainite	25
8	Martensitic microstructure of (a) normalized and heat treated, and (b) heat treated section of rotary forged hollow ESR ingot	26
9	Microstructure of reheat treated rotary forged hollow ESR cylinder	27
10	Flow lines at (a) OD, (b) mid-wall and (c) ID of vacuum degassed cylinder (Top)	28
11	Flow lines at (a) OD, (b) mid-wall and (c) ID of rotary forged vacuum degassed cylinder (Bottom)	28
12	Dendritic pattern at (a) OD, (b) mid-wall and (c) ID of rotary forged hollow ESR cylinder	29

INTRODUCTION

The Integrated Forging Line was used to produce experimental breech ring forgings for the advanced breech technology program. A hollow ESR cast cylinder was rotary forged and heat treated; subsequently, a forged hollow vacuum degassed cylinder was rotary forged and heat treated. In evaluating the material produced, anomalies appeared. This prompted the further, more detailed evaluation which is presented herein.

PRODUCTION OF FULL-SIZE CYLINDERS

Hollow ESR Ingot

The starting preform was a cast hollow ESR ingot of gun steel, produced by Cabot Corporation, with a nominal OD of 20" (actually tapered from 19-1/2" to 20-1/2") and a trepanned ID of 9.5". The original cast ID was 7.5". It was enlarged because the original intent was to use the ingot to produce a truncated 8" M201 tube. It was decided to use the material to produce a cylindrical forging from which to manufacture several breech rings. Previous experience with rotary forging of hollow ESR ingots was limited to the forging of one 105mm M68 tube from a smaller cast ingot, from which the results were comparable to those obtained with normal production rotary forge practice.

The preform was heated in the Cheston induction heating system and rotary forged over a 5.5" water cooled mandrel to an OD of approximately 17". Because of the large amount of sinking, i.e., free movement of the ID of the ingot prior to contacting the OD of the mandrel, the actual ID produced at each end was greater than 5.5". However, the preponderance of the ID contacted the mandrel during forging. The total forging reduction was very light, viz., about 1.15:1.

Heat treatment was performed in the Selas horizontal continuous heat treating system as shown in Table 1. In quenching hollow cylinders, the practice commonly used is to quench the ID first for a designated period (viz., ID Lead Time) and then quench both the ID and OD together for an extended period. In this case, the ID was quenched for approximately one minute longer than the OD. (Note: The ID is quenched by passing a large volume of water through the bore, whereas the OD is quenched by a water spray simultaneously along the entire length of the cylinder.)

After the initial heat treatment, a discard corresponding in length to one wall thickness was taken from each end and transverse mechanical properties measured at the mid-radius of the adjacent material. Because the results were unsatisfactory (Table 2), an additional discard was removed

from each end and material which definitely had contacted the mandrel during forging was tested. Unfortunately, this also was unsatisfactory (Table 2). The microstructure at the mid-wall of both the top and bottom showed evidence of ferrite and bainite (Figs. 1 and 2).

The inadequacy of the material can also be seen in the variation in longitudinal strength taken from the OD, mid-wall and ID of the initially heat treated cylinder (Table 3). An analysis of the microstructure at the OD, mid-wall and ID (Figure 3) suggested that the original heat treatment was inadequate in terms of both austenitizing and quenching.

There was evidence of ferrite showing that the cylinder had not been fully austenitized, and of bainite, showing that the material transformed to austenite had been inadequately quenched, since martensite is the desired product. Therefore, the remainder of the cylinder was passed through the Selsas system a second time at a slightly lower speed and tempered at a slightly lower temperature to raise the yield strength. Discards were removed, and the material was again tested. The results were still unsatisfactory in terms of mechanical properties (Table 2) and microstructure (Figure 4).

Additional material evaluation and testing were performed on smaller sections from the cylinder. These tests and results are described later.

Forged Vacuum Degassed Preform

Several forged vacuum degassed preforms were available for use in producing 8" M201 tube forgings as part of an MM&T program. Because of the lack of success with the hollow ESR, one was diverted to use in this program. It had been produced by National Forge Co. from a 61" ingot by press forging (solid) and machining into a hollow cylinder with nominal dimensions of 20" OD and 8.5" ID.

It was rotary forged into a 17" OD x 5.5" ID cylinder in the same manner as the hollow ESR ingot and heat treated in the Selas system as shown in Table 4.

After heat treating, a discard was taken from each end and the material was evaluated. The results were outstanding in terms of the combination of transverse mechanical properties obtained and in the consistency of the mechanical properties through the wall as shown by the longitudinal data (Table 5). The microstructures at both ends and through the wall show predominantly martensite at the OD with a larger amount of bainite at the mid-wall and ID (Figures 5 and 6). However, the yield strength was higher than

desired by about 10-11 ksi. Re-tempering in the Selas system to reduce the strength by such a small amount is extremely difficult. The tempering temperatures required are such that small changes can result in large changes in yield strengths. If the yield strength is reduced too much, then a complete re-heat treatment is required.

Therefore, a 30" section, sufficient to provide one breech ring and test material, was retempered at 1120°F for 3 hours at temperature in a standard furnace, and water quenched. The results were satisfactory (Table 6). Subsequently, three additional sections were reheat treated in the same fashion with similar satisfactory results (Table 6). (The yield strength obtained in Cylinder 2 suggests that that cylinder may have received a slightly different re-tempering treatment). The microstructure in all cases was a mixture of martensite and bainite (Figure 7).

Additional Work - Hollow ESR Ingot'

Because of the relatively poor properties and unusual microstructure obtained with the rotary forged hollow ESR ingot, several heat treating tests were conducted without additional forging. The problem appeared to be associated with several factors:

1. Structure and segregation in the ingot.
2. Very light forging reduction which did not break up the structure and segregation.
3. Very short time at relatively low austenitizing temperature, which is a feature of the Selas system, and in this case, appears to have been too short to completely austenitize the entire cross section because of the segregation.
4. Quenching practice which developed bainite rather than martensite.

The combination of these factors resulted in a macrostructure with a strong, coarse, dendritic pattern and a microstructure consisting of ferrite and bainite.

Initially, a one inch thick disc from the rotary forged cylinder was cut in half; one half was normalized and heat treated while the second half was heat treated without normalizing. After normalizing, both sections were heat treated together. The specimens were treated as follows:

Normalize (Section 1)

1700°F - 2 Hrs. - Air Cool

Harden (Both Sections)

1550°F - 1 Hr. (at temp) Water
Immersion Quench

Temper (Both Sections)

1100°F - 1 Hr. (at temp.) - Water
Immersion Quench

The mechanical properties were excellent (Table 7) and the microstructure was martensitic (Figure 8). The normalizing had no apparent effect.

To test the possibility of improving the properties in a full wall thickness, a 12" length of the cylinder was heat treated, with emphasis on extending the austenitizing time. The heat treatment was essentially the same as that for the non-normalized disc above, except that the austenitizing time, prior to hardening, was 6 hours. In this test there were two peculiarities. As shown in Table 8, a chordal section had been removed from the cylinder prior to heat treatment. Also, the quench was performed horizontally rather than vertically with the flat face being quenched first. Thus, Specimen 5, which is a mid-wall specimen from the forging standpoint, is actually an OD specimen as far as the quench is concerned. Also, Specimen 3 was subjected to a less than adequate quench because of the quenching technique. The mechanical properties obtained are also shown in Table 8. Despite the excellent mechanical properties, there is still evidence of ferrite and the

microstructure is predominantly bainite (Fig. 9) with the amount of ferrite being greater at the mid-wall which experienced the least forging deformation.

DISCUSSION AND CONCLUSIONS

The original intent of this work was to produce material which could be used for advanced technology breech rings. This was accomplished with the use of the vacuum degassed preform. Despite the fact that the rotary forge reduction was very light, the overall reduction from the ingot stage was heavy. Thus, as is seen in Figure 10, while there is evidence of a flow pattern, the cast structure is broken up, and the mid-wall is essentially the same as the ID and OD.

This is not true for the rotary forged hollow ESR ingot. There, the only forging reduction was that imposed during the rotary forge operation. As seen in Figure 11, this was not enough to break up the dendritic structure. Figure 12 also shows the uneven forging deformation experienced through the wall. This mid-wall shows less alignment of structure than the OD or ID, indicating less working.

While the residual cast structure undoubtedly contributes to the problematic mechanical properties obtained with the

hollow ESR, it is not acting alone. The final heat treatment test on the short full wall cylinder demonstrates that even with the light working, it is possible to develop outstanding mechanical properties.

The problem with the hollow ESR appears to be several fold. Ingot structure with an attendant segregation pattern is established during the solidification process. Heavy reduction, i.e., 3-5 to 1, should break up this structure and allow the generation of acceptable mechanical properties. This was demonstrated by the aforementioned 105mm M68 tube. However, light reductions do not break up the structure, nor affect the segregation pattern. This makes the development of good properties more difficult, but not impossible. When heat treated in the horizontal continuous furnace, where austenitizing temperatures are deliberately low and times are deliberately short, the residual ingot structure controls the mechanical properties. However, if austenitizing times can be increased significantly, and an adequate quench can be applied, a degree of homogenization can be developed, and outstanding properties can be generated, even at the mid-wall of heavy sections.

TABLE I
HOLLOW ESR
PROCESSING HISTORY

Starting Material - Cast hollow ESR ingot, 20" (nom.) OD
(as-cast) x 9.5" ID (machined). Produced by Cabot Corp.

Forging - Rotary Forge to 17" OD x 5.5" ID

Heat Treat - Heat treated in Selas System

Workpiece Speed - .12 Ft/min.

Austenitizing Exit Temp. - 1550°F - 1600°F

Water Spray Quench

ID Lead Time - 1 Min.

ID (Total) - 21 Min.*

OD (Total) - 20 Min.*

Tempering Temperature - 1125°F

Water Spray Cool

Reheat Treat - Reheat treated in Selas System

Workpiece speed - .11 Ft./min.

Austenitizing Exit Temp. - 1560°F - 1595°F

Water Spray Quench

ID Lead Time - 1 Min.

ID (Total) - 21 Min.

OD (Total) - 20 Min.

TABLE I (Continued)

Tempering Temperature - 1110°F

Water Spray Cool

*Originally quenched for 16 min. ID and 15 min. OD, then after a hardness check, quenched for an additional 5 min. on the OD and on the ID.

TABLE 2
HOLLOW ESR
ROTARY FORGED
SELAS HEAT TREAT

	YS	RA	C _v (-40°F)
1. Initial Heat Treat			
a. Initial Test			
Transverse - Top*	138 ksi	47%	18 ft-lbs
	144	45	19
	137	45	14
	138	45	14
Transverse - Bottom*	160	42	22
	145	41	32
	140	22	16
	140	39	19
b. Retest			
Transverse - Top	134	49	15
	138	48	17
Transverse - Bottom	136	41	15
	141	43	21
2. Reheat Treat			
Transverse - Top**	149	41	13
	159	43	9

*Top and Bottom signify the first and last ends through the rotary forge and the Selas heat treat system.

**Only one end tested.

TABLE 3
HOLLOW ESR
ROTARY FORGED
SELAS HEAT TREAT

	YS	RA	Cv(-40°F)
Longitudinal - Top			
OD	152 ksi	54%	51 ft-lbs
Mid	139	53	35
ID	152	59	44

TABLE 4
VACUUM DEGASSED
PROCESSING HISTORY

Starting material - Forged (from 61" ingot), machined
vacuum degassed preform, 20" OD x 8.5" ID.

Produced by National Forge Co.

Forging - Rotary Forge to 17" OD x 5.5" ID

Heat Treat - Heat treated in Selas System

Workpiece Speed - .11 ft/min.

Austenitizing Exit Temp. - 1550°F - 1590°F

Water Spray Quench

ID Lead Time - 1 min., 10 sec.

ID (Total) - 21 min., 10 sec.

OD (Total) - 20 min.

Tempering Temperature - 1100°F

Water spray cool

TABLE 5

VACUUM DEGASSED (FORGED)
 ROTARY FORGED
 SELAS HEAT TREAT

	YS	RA	C _V (-40°F)
Transverse - Top*	151 ksi 158	47% 42	34 ft-lbs. 31
Transverse - Bottom*	156 154	43 44	37 37
Longitudinal - <u>Top*</u>			
OD	159 159	61 64	57 55
MID	159 159	62 61	58 58
ID	159 159	63 63	53 54
Longitudinal - <u>Bottom*</u>			
OD	155 154	62 63	58 62
MID	155 155	62 63	61 60
ID	156 155	62 65	61 57

*Top and Bottom signify the first and last ends through the rotary forge and the Selas heat treat system.

TABLE 6
VACUUM DEGASSED (FORGED)
ROTARY FORGED
SELAS HEAT TREAT
RETEMPER - STANDARD FURNACE

	YS	RA	C _v (-40°F)
Cylinder 1 - Transverse	148 ksi	47%	40 ft-lbs.
	150	47	38
Longitudinal	154	64	55
	150	63	63
Cylinder 2 - Transverse	156	44	39
	154	41	39
Cylinder 3 - Transverse	149	49	38
	150	35	42
Cylinder 4 - Transverse	148	48	46
	146	51	40

Retemper each piece - 1120°F - 3 Hrs. at temp.

#1, 2 - 30" long cylinder

3, 4 - 26" long cylinder


TABLE 7
HOLLOW ESR
ROTARY FORGED
SELAS HEAT TREAT
REHEAT TREATED IN SMALL SECTIONS


	YS	RA	C _v (-40°F)
Transverse			
Normalized	166 ksi 164	46% 45	35 ft-lbs 32
Not Normalized	162 161	49 47	39 37

TABLE 8


HOLLOW ESR
ROTARY FORGED
SELAS HEAT TREAT
REHEAT TREATED IN FULL WALL THICKNESS SECTIONS

SPECIMEN	YS	RA	C _v
1	152 ksi	52%	44 ft-lbs.
2	152	44	41
3	150	36	28
4	150	39	39
5	153	39	39

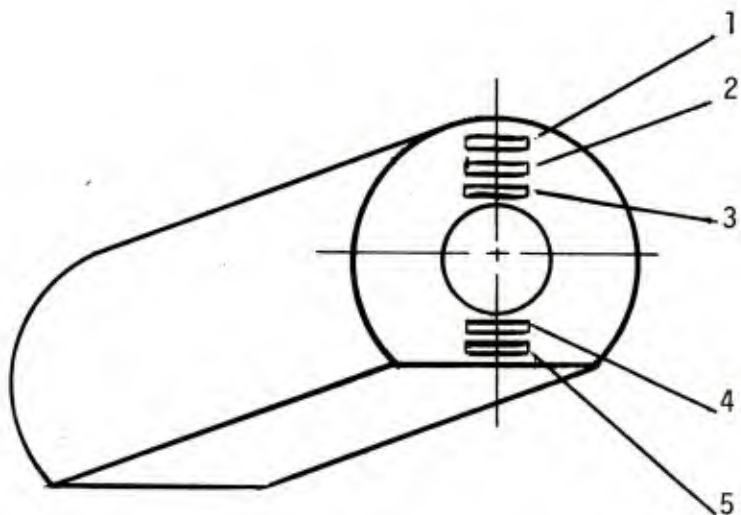

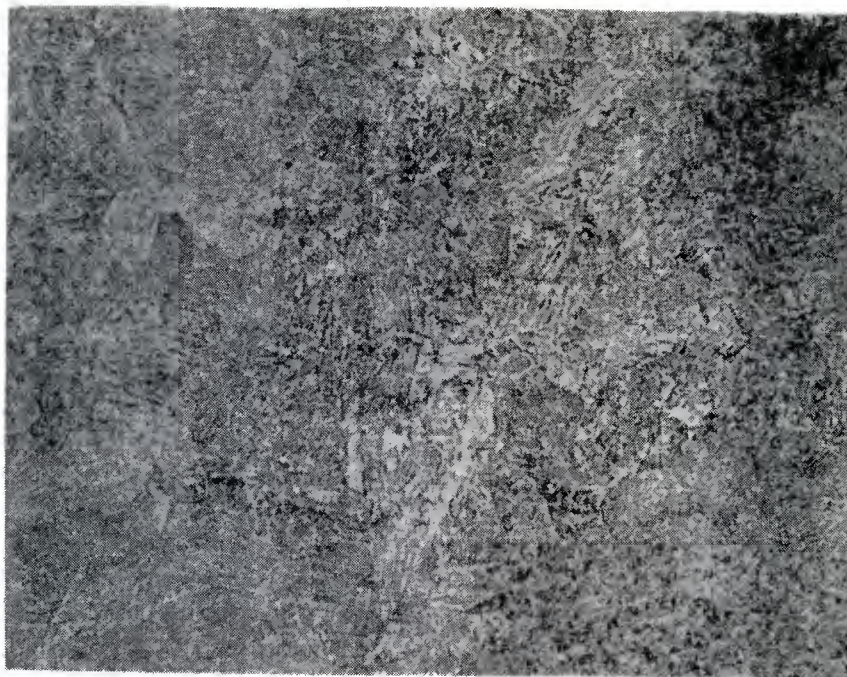

1(a) - Ferrite patches

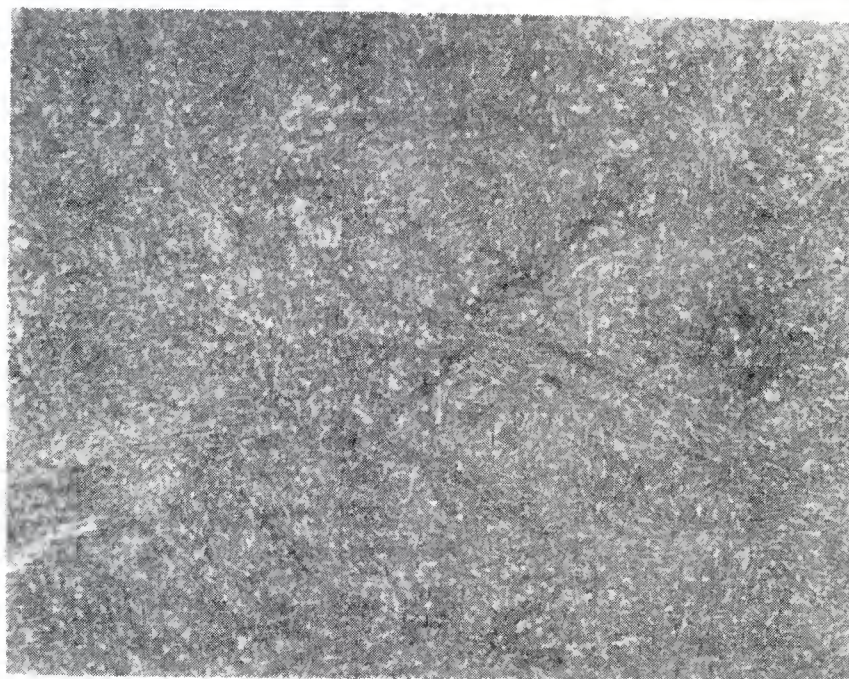


1(b) - Predominantly bainite

FIG. 1 - Microstructure at mid-wall of heat treated rotary forged hollow ESR Cylinder (Top) - 1000X
(See Table 2)



2(a) - Ferrite patches

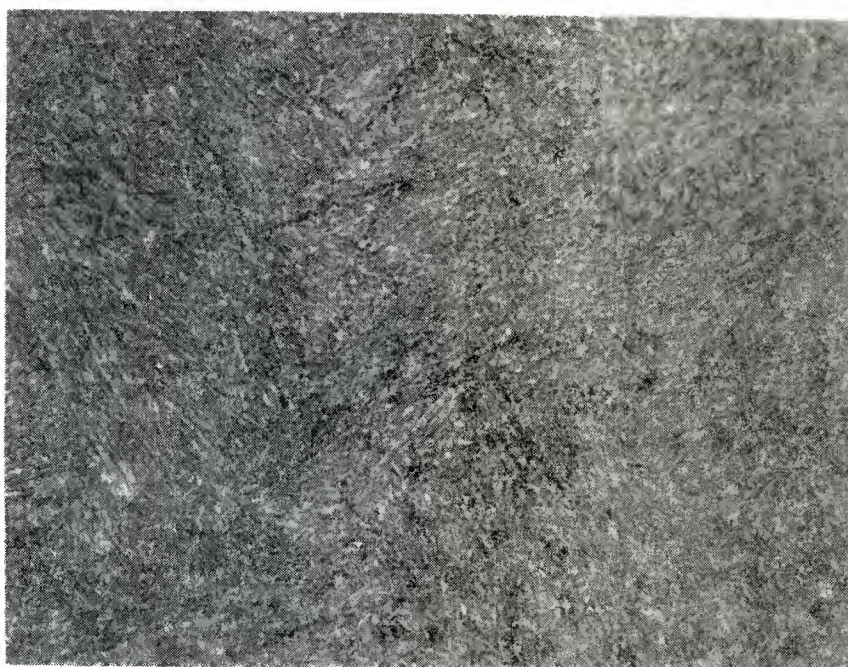


2(b) - Predominantly bainite

FIG. 2 - Microstructure at mid-wall of heat treated rotary forged hollow ESR cylinder (Bottom) - 1000X
(See Table 2)



3(a) OD - Predominantly bainite

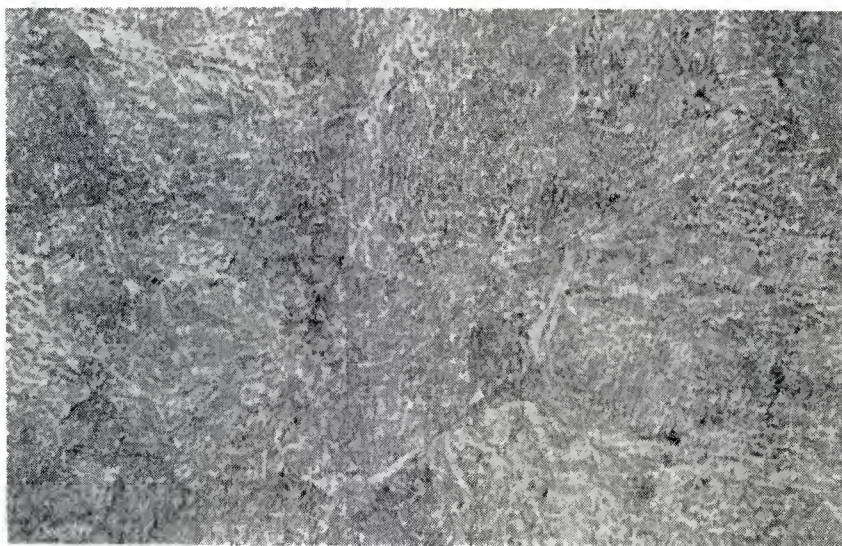

3(b) Mid-wall - Ferrite patches




3(c) ID - Predominantly bainite


FIG. 3 - Microstructure of heat treated rotary forged hollow ESR cylinder (Top) - 1000X (See Table 3)




FIG. 4 - Microstructure at mid-wall of reheat treated rotary forged hollow ESR cylinder (Top) - 100CX (See Table 2)

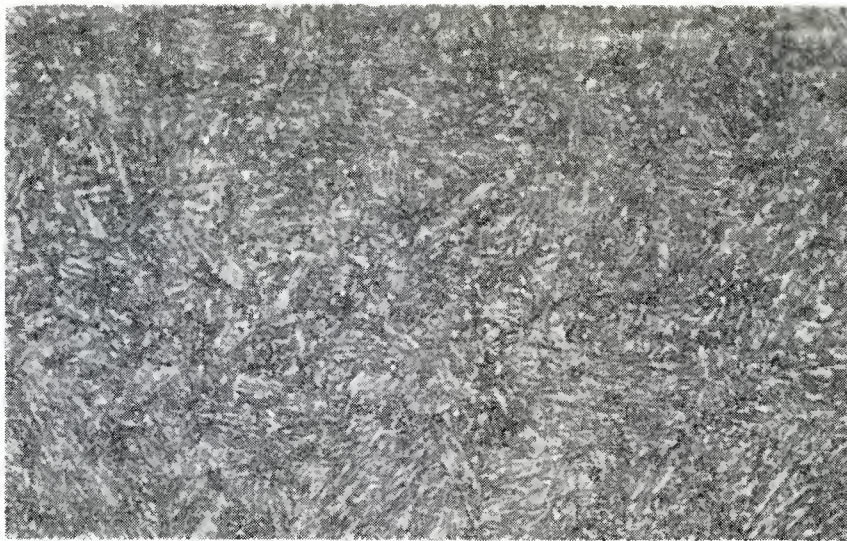

5(a) OD - Martensite - Bainite

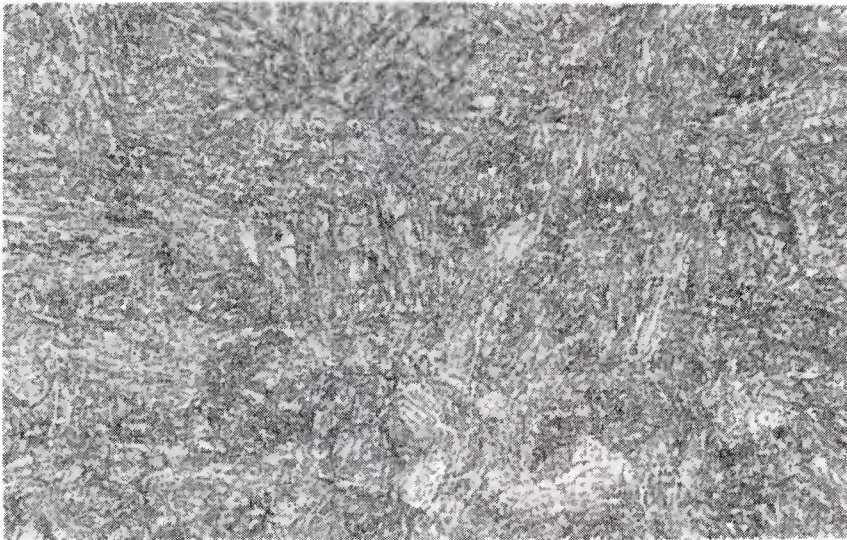

5(b) Mid-wall - Martensite - Bainite

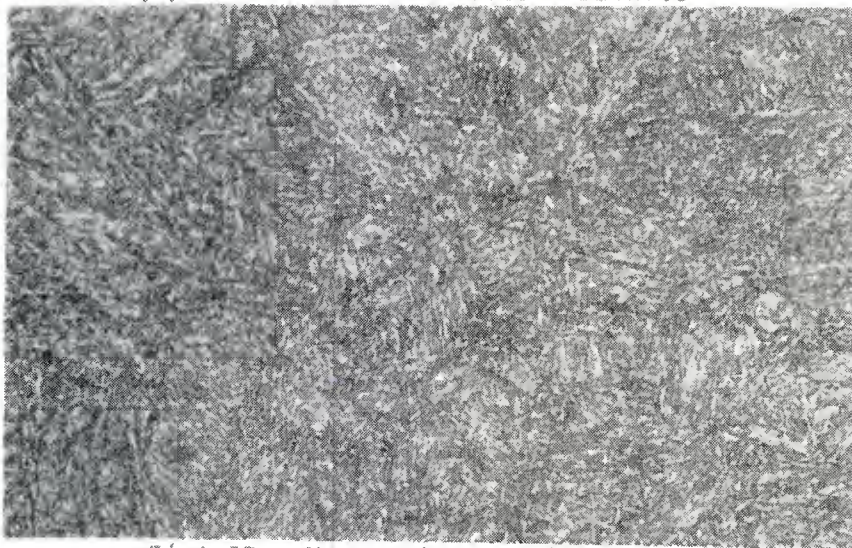

5(c) ID - Martensite - Bainite


FIG. 5 - Microstructure of heat treated rotary forged vacuum degassed cylinder (Top) - 1000X (See Table 5)



6(a) OD - Martensite - Bainite




6(b) Mid-wall - Martensite - Bainite

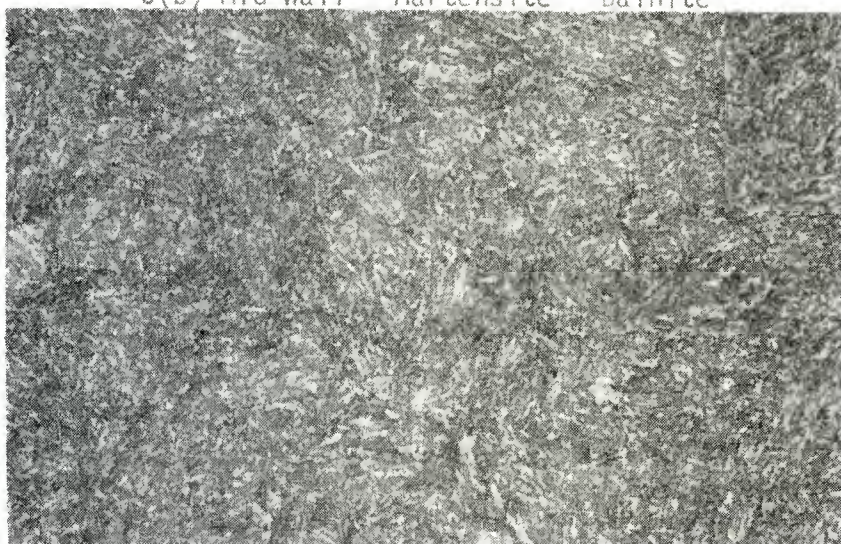


6(c) ID - Martensite - Bainite


FIG. 6 - Microstructure of heat treated rotary forged vacuum degassed cylinder (Bottom) - 1000X (See Table 5)

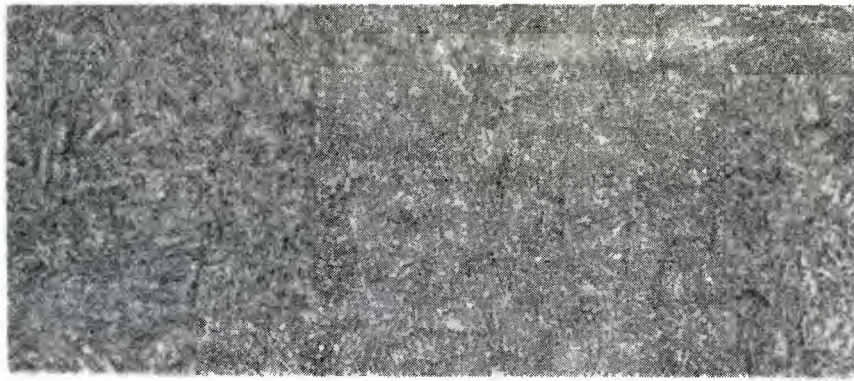


7(a) Cylinder 1

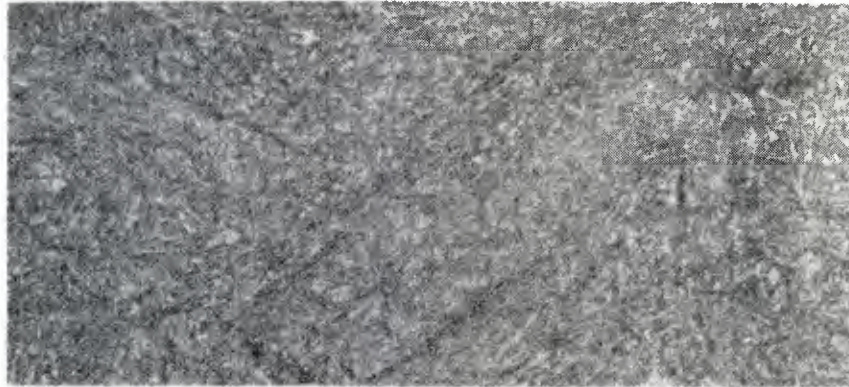

7(b) Cylinder 2

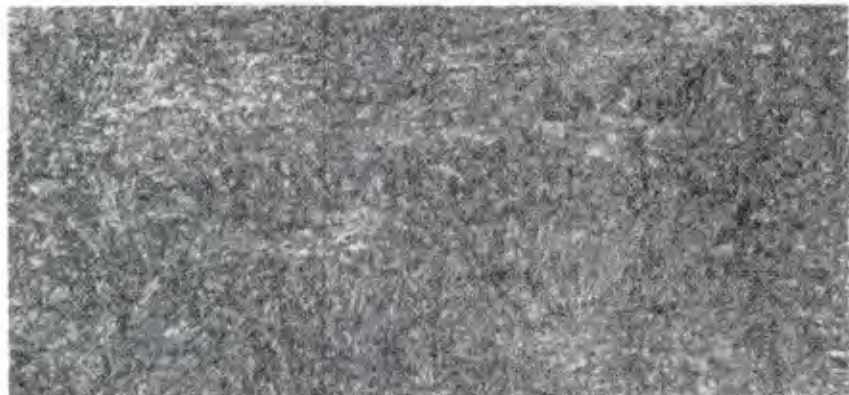


7(c) Cylinder 3

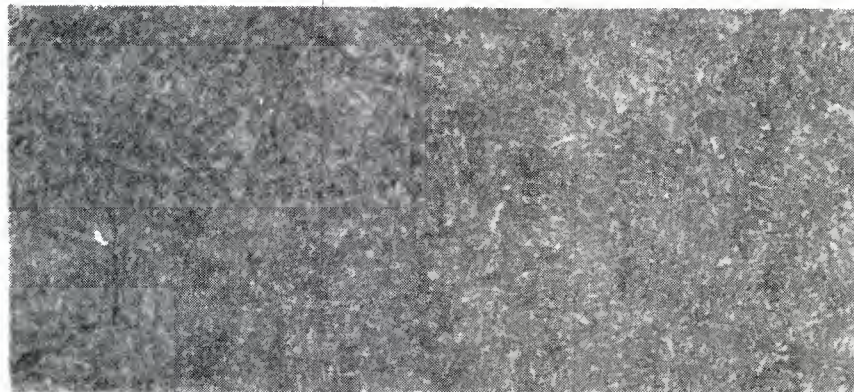


7(d) Cylinder 4

FIG. 7 - Microstructure at mid-wall of reheat treated rotary forged cylinders - Martensite-Bainite 1000X (See Table 6)

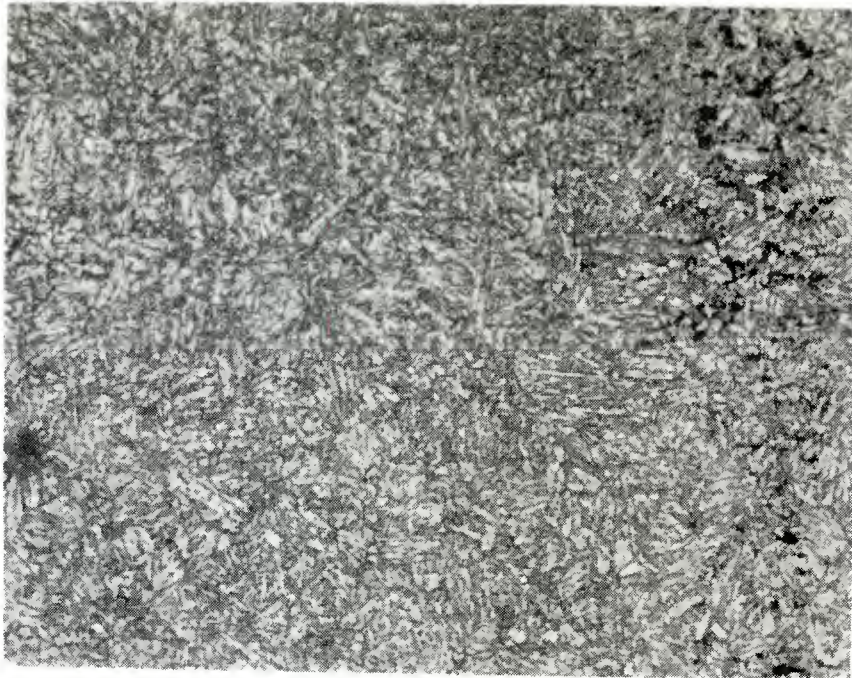


8(a) Normalized

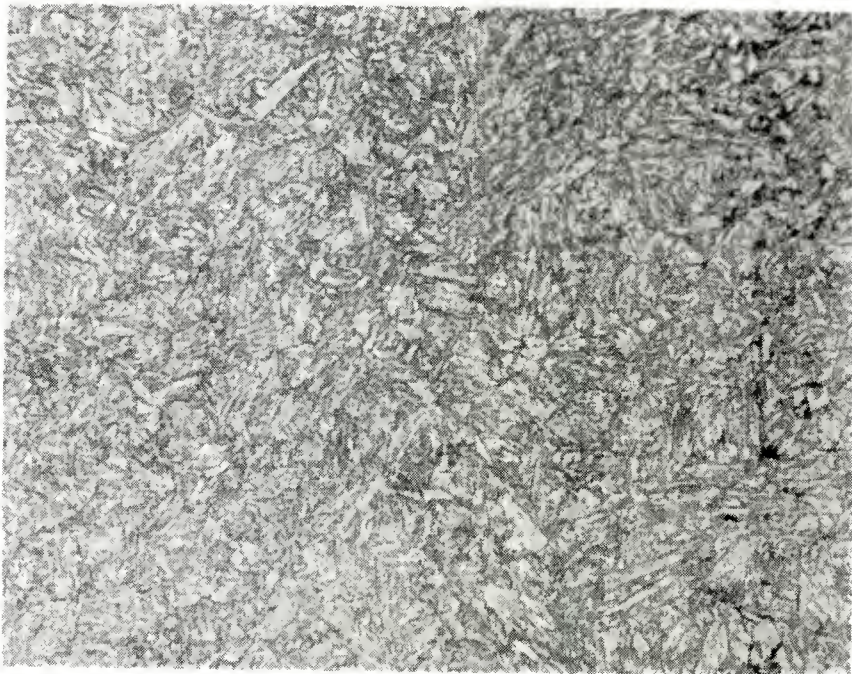

8(b) Not Normalized

FIG. 8 - Martensitic microstructure of (a) normalized and heat treated, and (b) heat treated section of rotary forged hollow ESR ingot - 1000X (See Table 7)

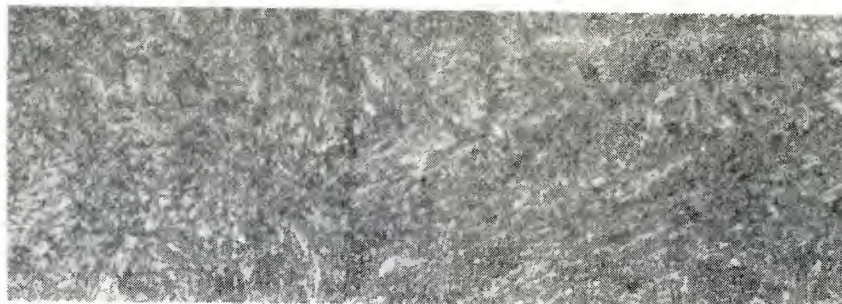


9(a) Section 9-1 - Martensite-Bainite




9(b) Section 9-2 - Ferrite Patches



9(c) Section 9-3 - Ferrite Patches

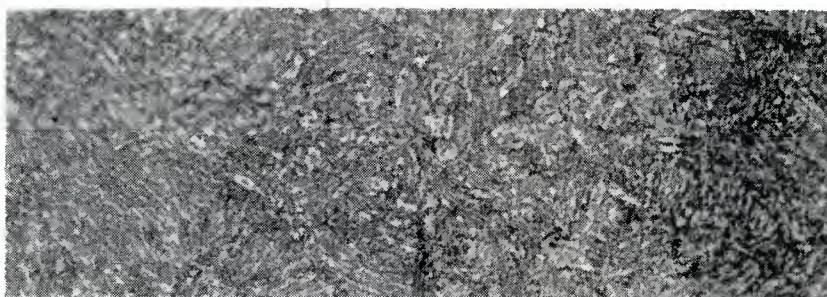

9(d) Section 9-4 - Martensite-Bainite

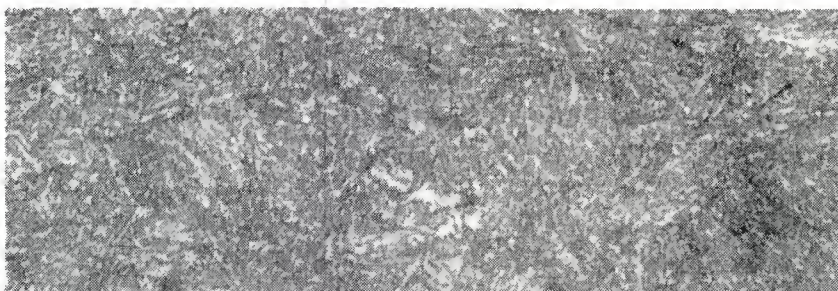

9(e) Section 9-5 - Martensite-Bainite


FIG. 9 - Microstructure of reheat treated rotary forged hollow ESR cylinder - 1000X (See Table 8)



10(a) OD



10(b) Mid-wall

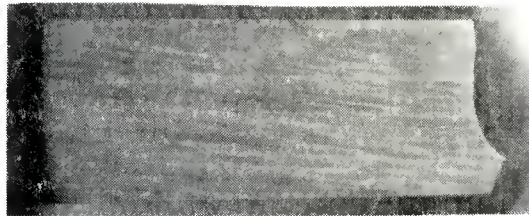

10(c) ID

FIG. 10 - Flow lines at (a) OD, (b) Mid-wall and (c) ID of vacuum degassed cylinder (Top).



11(a) OD



11(b) Mid-wall



11(c) ID

FIG. 11 - Flow lines at (a) OD, (b) Mid-wall and (c) ID of rotary forged vacuum degassed cylinder (Bottom).



12(a) OD



12(b) Mid-wall



12(c) ID

FIG. 12 - Dendritic pattern at (a) OD, (b) Mid-wall and (c) ID of rotary forged hollow ESR cylinder. (Note the greater compaction of the pattern at the OD indicating an uneven deformation during forging.)

WATERVLIET ARSENAL INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
COMMANDER	1
DIRECTOR, BENET WEAPONS LABORATORY	1
CHIEF, DEVELOPMENT ENGINEERING BRANCH	1
ATTN: DRDAR-LCB-DA	1
-DM	1
-DP	1
-DR	1
-DS	1
-DC	1
CHIEF, ENGINEERING SUPPORT BRANCH	1
CHIEF, RESEARCH BRANCH	2
ATTN: DRDAR-LCB-RA	1
-RC	1
-RM	1
-RP	1
TECHNICAL LIBRARY	5
TECHNICAL PUBLICATIONS & EDITING UNIT	2
DIRECTOR, OPERATIONS DIRECTORATE	1
DIRECTOR, PROCUREMENT DIRECTORATE	1
DIRECTOR, PRODUCT ASSURANCE DIRECTORATE	1

NOTE: PLEASE NOTIFY DIRECTOR, BENET WEAPONS LABORATORY, ATTN: DRDAR-LCB-TL, OF ANY REQUIRED CHANGES.

EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
ASST SEC OF THE ARMY RESEARCH & DEVELOPMENT ATTN: DEP FOR SCI & TECH THE PENTAGON WASHINGTON, D.C. 20315	1	COMMANDER US ARMY TANK-AUTMV R&D COMD ATTN: TECH LIB - DRDTA-UL MAT LAB - DRDTA-RK WARREN, MICHIGAN 48090	1 1
COMMANDER US ARMY MAT DEV & READ. COMD ATTN: DRCDE 5001 EISENHOWER AVE ALEXANDRIA, VA 22333	1	COMMANDER US MILITARY ACADEMY ATTN: CHMN, MECH ENGR DEPT WEST POINT, NY 10996	1
COMMANDER US ARMY ARRADCOM ATTN: DRDAR-TSS DRDAR-LCA (PLASTICS TECH EVAL CEN)	2 1	COMMANDER REDSTONE ARSENAL ATTN: DRSMI-RB DRSMI-RRS DRSMI-RSM ALABAMA 35809	2 1 1
DOVER, NJ 07801			
COMMANDER US ARMY ARRCOM ATTN: DRSAR-LEP-L ROCK ISLAND ARSENAL ROCK ISLAND, IL 61299	1	COMMANDER ROCK ISLAND ARSENAL ATTN: SARRI-ENM (MAT SCI DIV) ROCK ISLAND, IL 61202	1
DIRECTOR US ARMY BALLISTIC RESEARCH LABORATORY ATTN: DRDAR-TSB-S (STINFO) ABERDEEN PROVING GROUND, MD 21005	1	COMMANDER HQ, US ARMY AVN SCH ATTN: OFC OF THE LIBRARIAN FT RUCKER, ALABAMA 36362	1
COMMANDER US ARMY ELECTRONICS COMD ATTN: TECH LIB FT MONMOUTH, NJ 07703	1	COMMANDER US ARMY FCN SCIENCE & TECH CEN ATTN: DRXST-SD 220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	1
COMMANDER US ARMY MOBILITY EQUIP R&D COMD ATTN: TECH LIB FT BELVOIR, VA 22060	1	COMMANDER US ARMY MATERIALS & MECHANICS RESEARCH CENTER ATTN: TECH LIB -DRXMR-PL WATERTOWN, MASS 02172	2

NOTE: PLEASE NOTIFY COMMANDER, ARRADCOM, ATTN: BENET WEAPONS LABORATORY, DRDAR-LCB-TL, WATERVLIET ARSENAL, WATERVLIET, N.Y. 12189, OF ANY REQUIRED CHANGES.

EXTERNAL DISTRIBUTION LIST (CONT)

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
COMMANDER US ARMY RESEARCH OFFICE P.O. BOX 1211 RESEARCH TRIANGLE PARK, NC 27709	1	COMMANDER DEFENSE DOCU CEN ATTN: DDC-TCA CAMERON STATION ALEXANDRIA, VA 22314	12
COMMANDER US ARMY HARRY DIAMOND LAB ATTN: TECH LIB 2800 POWDER MILL ROAD ADELPHIA, MD 20783	1	METALS & CERAMICS INFO CEN BATTELLE COLUMBUS LAB 505 KING AVE COLUMBUS, OHIO 43201	1
DIRECTOR US ARMY INDUSTRIAL BASE ENG ACT ATTN: DRXPE-MT ROCK ISLAND, IL 61201	1	MPDC 13919 W. BAY SHORE DR. TRAVERSE CITY, MI 49684	1
CHIEF, MATERIALS BRANCH US ARMY R&S GROUP, EUR BOX 65, FPO N.Y. 09510	1	MATERIEL SYSTEMS ANALYSIS ACTV ATTN: DRXSY-MP ABERDEEN PROVING GROUND MARYLAND 21005	1
COMMANDER NAVAL SURFACE WEAPONS CEN ATTN: CHIEF, MAT SCIENCE DIV DAHLGREN, VA 22448	1		
DIRECTOR US NAVAL RESEARCH LAB ATTN: DIR, MECH DIV CODE 26-27 (DOC LIB) WASHINGTON, D.C. 20375	1 1		
NASA SCIENTIFIC & TECH INFO FAC P.O. BOX 8757, ATTN: ACQ BR BALTIMORE/WASHINGTON INTL AIRPORT MARYLAND 21240	1		

NOTE: PLEASE NOTIFY COMMANDER, ARRADCOM, ATTN: BENET WEAPONS LABORATORY, DRDAR-LCB-TL, WATERVLIET ARSENAL, WATERVLIET, N.Y. 12189, OF ANY REQUIRED CHANGES.