

AD-A075 812

TEXAS UNIV AT AUSTIN DEPT OF CHEMISTRY

F/G 20/12

SEMICONDUCTOR ELECTRODES 25. THE P-6AAS/HEPTYL VIIOLOGEN SYSTEM.


OCT 79 B REICHMAN , F F FAN , A J BARD

N00014-78-C-0592

UNCLASSIFIED TR-2

NL

1 OF 1
AD
A075812



END
DATE
FILMED
11-79
DDC

12

OFFICE OF NAVAL RESEARCH

Contract ¹⁵ N00014-78-C-0592

Task No. NR 051-693

TECHNICAL REPORT No. 2

LEVEL ^H

AD A 075812

⁶ Semiconductor Electrodes, 25.
The p-GaAs/Heptyl Viologen System.
Photoelectrochemical Cells and
Photoelectrochromic Displays.

by

¹⁰ Benjamin Reichman, Fu-Ren F. Fan and Allen J. Bard

Prepared for Publication

in the

¹² ³⁰ Journal of the Electrochemical Society ¹¹ 1 Oct 79

⁹ Technical rept. 1 Sep 79-31 Aug 80,

¹⁴ TR-2

The University of Texas at Austin
Department of Chemistry
Austin, Texas 78712

October 1, 1979

DDC
RECEIVED
OCT 31 1979
RECEIVED
A

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

DDC FILE COPY

79 10 31 026

347 830

slh

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 2	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Semiconductor Electrodes 25. The p-GaAs/Heptyl Viologen System. Photoelectrochemical Cells and Photoelectrochromic Displays.		5. TYPE OF REPORT & PERIOD COVERED 1 Sept. 1979 to 31 Aug. 1980
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Benjamin Reichman, Fu-Ren F. Fan and Allen J. Bard		8. CONTRACT OR GRANT NUMBER(s) N00014-78-C-0592
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry University of Texas at Austin Austin, TX 78712		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research 800 N. Quincy Arlington, VA 22217		12. REPORT DATE October 1, 1979
		13. NUMBER OF PAGES 30
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; its distribution is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Prepared for publication in the Journal of the Electrochemical Society.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) semiconductors photoelectrochemistry electrochromic displays		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The photoreduction of aqueous solutions of 1,1'-diheptyl-4,4'-bipyridyl (heptyl viologen, HV^{2+}) bromide on p-GaAs was investigated. Under irradiation with light of wavelengths below 885 nm, the photoreduction of HV^{2+} to form a precipitate of violet $HVBr$ occurs on p-GaAs at a potential of ~ 400 mV more positive than the reversible potential of the $HV^{2+}/HVBr$ couple on Pt. Oxidation of $HVBr$ back to soluble HV^{2+} occurs in the dark at more negative potentials. Photoelectrochemical low capacity storage cells based on this reaction		

DD FORM 1473
1 JAN 73EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601Unclassified
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

with Cu, Ni, or $H_xNb_2O_5$ counter electrodes were constructed. In such cells, under illumination, the p-GaAs electrode behaves as the cathode, a photovoltage develops and current flows in the external circuit, while H₂Br precipitates on the electrode surface and the counter electrode is oxidized. In the dark, the current flows in the opposite direction, the p-GaAs is the anode and reduction occurs at the counter electrode. Such a cell also produces an alternating electrical output under periodic illumination. Photoelectrochromic cells based on this reaction and utilizing simultaneous addressing with light and electrical signals are also proposed. ↩

Semiconductor Electrodes 25. The p-GaAs/Heptyl Viologen
System. Photoelectrochemical Cells and
Photoelectrochromic Displays.

Benjamin Reichman, Fu-Ren F. Fan and Allen J. Bard*

Department of Chemistry

The University of Texas at Austin

Austin, Texas 78712

*Electrochemical Society Active Member

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist.	Avail and/or special
A	

(ABSTRACT)

The photoreduction of aqueous solutions of 1,1'-diheptyl-4,4'-bipyridyl (heptyl viologen, HV^{2+}) bromide on p-GaAs was investigated. Under irradiation with light of wavelengths below 885 nm, the photoreduction of HV^{2+} to form a precipitate of violet HVBr occurs on p-GaAs at a potential of ~ 400 mV more positive than the reversible potential of the $HV^{2+}/HVBr$ couple on Pt. Oxidation of HVBr back to soluble HV^{2+} occurs in the dark at more negative potentials. Photoelectrochemical low capacity storage cells based on this reaction with Cu, Ni, or $H_xNb_2O_5$ counter electrodes were constructed. In such cells, under illumination, the p-GaAs electrode behaves as the cathode, a photovoltage develops and current flows in the external circuit, while HVBr precipitates on the electrode surface and the counter electrode is oxidized. In the dark,


the current flows in the opposite direction, the p-GaAs is the anode and reduction occurs at the counter electrode. Such a cell also produces an alternating electrical output under periodic illumination. Photoelectrochromic cells based on this reaction and utilizing simultaneous addressing with light and electrical signals are also proposed.

(End of Abstract)

INTRODUCTION

A number of photoelectrochemical (PEC) cells employing semiconductor electrodes for the conversion of radiant to electrical energy (liquid junction photovoltaic cells) have been described (1-17). Most have employed n-type semiconductors and have been used for the instantaneous production of electricity without chemical storage. The possibility of a photochargeable PEC cell using a third storage electrode or with production of soluble reactants has been discussed however (8,10-11). PEC cells employing p-type electrodes are less common (8-9,15-17). Studies of aqueous systems with p-GaAs and p-GaP have been reported, (15-16,18) but the observed efficiencies of these were usually quite small and in many cases problems with electrode stability were encountered. Investigations of p-GaAs electrodes in acetonitrile solutions suggest good stability under strict water-free conditions (19).

We report here investigations of the p-GaAs electrode immersed in aqueous solutions containing 1,1'-diheptyl-4,4'-bipyridyl (heptyl viologen, HV^{2+}) bromide. The reduction of HV^{2+} bromide on metal electrodes yields a

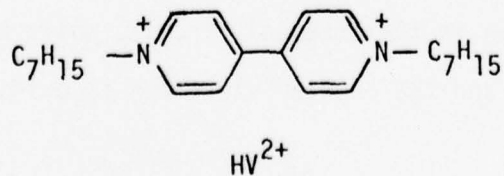

precipitate of the violet radical cation salt (eq. [1]) and this has been



suggested as the basis of electrochromic displays (20-22). The formation of such a precipitate by photoreduction at a p-type semiconductor would allow low capacity energy storage via a solid material, just as occurs in secondary batteries. We will show that such a photoreduction does occur at p-GaAs at potentials ~ 400 mV less negative than that observed at a platinum electrode and that dark oxidation of the HVBr precipitate is possible. Moreover the p-GaAs electrode is stable both in the dark and under illumination in the HV^{2+} solution so that PEC cells using suitable counter electrodes (e.g., Cu/CuO) which show a periodic electrical output under chopped illumination can be constructed.

A second aspect of these studies concerns the application of reaction [1] on p-GaAs for display purposes. Several devices for active displays based on combining electrogenerated chemiluminescence and semiconductors have been described (23). A passive photoactivated display based on metal deposition on a semiconductor electrode was recently reported (24). The principles of a similar display based on precipitation of HVBr at a point on a semiconductor electrode simultaneously addressed by light and an electrical signal is described here.

EXPERIMENTAL

The single crystal p-GaAs was obtained from Atomergic Chemicals (Long Island, N.Y.) with acceptor concentration $3 \times 10^{18} \text{ cm}^{-3}$ (Zn-doped) and was mounted as an electrode as previously described (13). The surface (face 111) was first polished with $0.5 \mu\text{m}$ alumina powder and then etched for 10-15 sec in a solution which contained $\text{H}_2\text{SO}_4:\text{H}_2\text{O}:30\% \text{H}_2\text{O}_2$ in concentration ratio 3:1:1. In some

experiments single crystal p-GaP was also employed. The surface of this crystal was etched in 11 M HCl for 10 sec before use.

As light sources either a 450 W xenon lamp or a He-Ne laser (1.6 mW power) was used. The potentiostatic measurements were carried out with a Princeton Applied Research (PAR) potentiostat Model 173, with a cell consisting of an aqueous saturated calomel reference electrode (S.C.E.) and a Pt wire as the counter electrode. The electrochemical cell was provided with pyrex windows for the passage of light. Nitrogen gas was passed through the solution before the experiments and above the solution during the experiments, since viologen radical cations are very sensitive to oxygen.

In the two electrode PEC cell experiments the voltage of the photocell between the p-GaAs and the oxide counter electrode was measured on a x-t recorder through a voltage follower. The photocell current was measured on an x-t recorder through a current-to-voltage-converter. For short time measurements of the cell short circuit current, a Nicolet Model 1090A digital oscilloscope was used. The light intensity at the semiconductor surface was varied by means of neutral density filters.

RESULTS

Cyclic voltammetry. The i - V curve at a p-GaAs electrode of an unstirred solution of 0.01 M HV^{2+} and 0.2 M KBr at a scan rate of 100 mV/sec is shown in Fig. 1. In the dark (curve a) there was only a small current in the cathodic region with a very small peak on scan reversal. Under illumination of the p-GaAs electrode surface with the full power of the 450 W xenon lamp, a larger cathodic current beginning at ~ 0.1 V vs. S.C.E. appeared (curve b). Simultaneously with the appearance of this cathodic current, the precipitation of the violet $HVBr$ was observed on the electrode surface. On reversing the

scan direction, a sharp anodic current peak occurred, either in the dark or under illumination. During the passage of the anodic current the violet precipitate on the semiconductor surface disappeared. Thus the overall process is that shown in [1], with illumination necessary for the reduction process, as is usual for p-type semiconductors.

These cyclic voltammograms could be repeated many (at least 100) times with only a small change in the peak height of the cathodic photocurrents, demonstrating good chemical reversibility of the deposition and stripping process. Upon illuminating the electrode with the narrow beam of a He-Ne laser, violet spots appeared on the electrode surface at exactly the location and of the size of the laser beam spot. The response time of the process was investigated by potential steps under illumination or by irradiation with chopped light with the electrode held at a constant potential (Fig. 2). A good coloration was observed on the electrode surface within ~ 0.5 sec after illumination of the electrode. Although the intensity ratio for HVBr deposited on dark p-GaAs is not very high, the deposition was easily discernable and this type of process can be considered for use as an electrochromic display controlled by both light and electrode potential and may also be applicable to photoimaging purposes (24-25).

The cyclic voltammograms of the solution of 0.01 M HV^{2+} dibromide and 0.2 M KBr at a Pt electrode is shown in Fig. 1c. By comparison of this voltammogram with that obtained with p-GaAs under illumination, one can see that significant photoreduction of HV^{2+} can occur on p-GaAs at potentials ~ 400 mV less negative than on Pt. The photocurrent attributable to the reduction of protons on the p-GaAs in a KBr solution not containing HV^{2+} was very small (Fig. 1d). Photoreduction of HV^{2+} was also investigated with a p-GaP photocathode. In this case the underpotential for the reduction

process was even larger than in the case of p-GaAs, but the process was not very reversible and the back oxidation occurred only at more positive potentials than on a Pt electrode. Thus upon scanning a p-GaP electrode over roughly the same potential region (Fig. 3), a gradual accumulation of HVBr occurred on the electrode surface and the cathodic current gradually decreased.

With the light intensity used in the experiments described above the photoreduction current on p-GaAs was limited by the rate of diffusion of HV^{2+} to the electrode surface, as demonstrated by the proportionality of the cathodic photocurrent to the square root of the scan rate, v (Fig. 4). Moreover, as shown in Fig. 5, while the potential for photocurrent onset and the current at the foot of the wave depended upon the light intensity, at more negative potentials the maximum current was almost independent of intensity and was limited by the rate of diffusion of HV^{2+} to the electrode surface.

PEC cells. Since the photoreduction of HV^{2+} occurs on p-GaAs with an underpotential of about 400 mV while the back-oxidation in the dark on p-GaAs occurs at the same potentials as on Pt, one can envision a sort of solar storage cell composed of a p-GaAs and another chemically reversible electrode (Fig. 6). This counter electrode should have a redox potential between the potential for the photoreduction of HV^{2+} on p-GaAs and the potential for oxidation of HVBr in the dark (Fig. 6c). In such a cell, when light irradiates the p-GaAs, it is the cathode of the cell and HVBr precipitates (Fig. 6a). The HVBr precipitate on the p-GaAs is stable at open circuit and can be oxidized in the dark back to the original HV^{2+} while the counter electrode becomes the cathode of the cell (Fig. 6b). Three counter electrodes with redox potentials suitable for such a photocell, Cu/Cu-oxide, $H_xNb_2O_5/Nb_2O_5$, and Ni/Ni-oxide, were used. The open circuit voltages and the short circuit currents of such

cells composed of p-GaAs and the three counter electrodes under periodic illumination are shown in Fig. 7. The relative polarity of the p-GaAs shows the expected changes (Fig. 6) as the semiconductor is subjected to the chopped beam. In the photocharged condition, the HVBr remained on the electrode surface and the open circuit voltage was stable for at least 2 hr. The maximum open circuit voltages were found with the Cu counter electrode with potential excursions of up to 0.4 V observed (Fig. 7A). The short circuit currents of these cells are shown in Fig. 7B. In the light, current flows in the external circuit during which precipitation of the purple HVBr on the surface of the p-GaAs occurs. The current decays almost to zero in about 10 sec because a thick opaque film of HVBr builds up on the electrode surface and the HV^{2+} concentration is depleted near the electrode surface. The cell can be regarded as a storage battery. The precipitate of HVBr can be stored on the p-GaAs and then oxidized in the dark to yield a current in a direction opposite to that observed under illumination. Obviously the capacity of such a cell is very small; the maximum charge in the form of HVBr which can precipitate on the p-GaAs before the current drops to zero is about 10 mC/cm^2 . Alternately, the cell can be considered as a type of a.c. device under periodic illumination. In this mode the p-GaAs cell performance was very stable with all three cells and no deterioration or decrease in the current were observed after 4 days of continuous operation with 20 sec period illumination by the 450 W xenon lamp. The open circuit voltage, the current and the amount of charge involved were all reproducible and stable to within 10%. The variation of the initial short circuit current on light intensity under irradiation with the He-Ne Laser (1.6 mW power) was examined with all three cells (Fig. 8). A linear dependence of the short circuit current on light intensity was observed at the lower intensity levels. In the case of Cu counter electrode, saturation of the current occurred at $\sim 2.5 \text{ mA/cm}^2$. With Ni as the counter electrode, no

saturation of the short circuit current occurred even at the highest intensity used, while with Nb_2O_5 as a counter electrode a linear dependence was observed only at very low light levels. In all cases the currents obtained were the highest for the Cu electrode. The current saturation observed in this case can probably be ascribed to the limitation by diffusion of HV^{2+} to the p-GaAs surface, since the magnitude of the saturation current density in Fig. 8a is similar to the limiting current found in the voltammograms, Fig. 1b, with identical HV^{2+} concentrations. With the Nb_2O_5 electrode the short circuit current reaches saturation earlier than in the case of Cu and was clearly limited by the oxidation reaction taking place on the Nb_2O_5 electrode. The maximum quantum efficiencies for the photocells were calculated from the slopes of the linear portions of the curves in Fig. 8, yielding values of $\sim 20\%$ (Cu), $\sim 10\%$ (Ni), and 2% (Nb_2O_5).

DISCUSSION

The behavior of the p-GaAs/solution interface and a rationalization of the observed PEC cell behavior can be presented in terms of the surface controlled model for GaAs proposed elsewhere (26) (Fig. 9). In this model the Fermi level of the semiconductor is pinned by surface states located about one-third of the way up in the gap (i.e., ~ 0.4 to 0.5 V above the valence band edge) (Fig. 9a). The maximum open circuit photopotential, V_{on} , observed under intense illumination would then be ~ 0.4 V, and the open circuit photovoltage would be the difference between V_{on} and V_{redox} of the counter electrode reaction (Fig. 9b). In the dark after deposition of HVBr , oxidation of HVBr occurs via the surface states and the p-GaAs essentially behaves as an inert contact to the layer (Fig. 9c). The counter electrode in a two-electrode

PEC cell must have a redox potential between V_{on} and that of the $HV^{2+}/HVBr$ system, so that only couples in a relatively narrow range of potentials are suitable.

Storage cells based on this type of electrode reaction will necessarily have small capacities unless films which deposit on the electrode surface can be found which are both transparent to the wavelengths absorbed by the semiconductor and are electrical conductors. Moreover higher concentrations of the soluble form are required to prevent mass transfer limitations to the photocurrent even before film formation causes current decay. Such cells may however find application in very low capacity batteries or as a.c. devices under periodic illumination.

The application of such a system to produce a display addressable both optically and electrically (a photoelectrochromic display) is perhaps of greater interest (Fig. 10). One can envision the operation of such a device in which a light beam produces a raster on the electrode surface and the electrode potential is switched to (a) the deposition potential (coloring), (b) open circuit (hold), or (c) the stripping potential (erase). The advantage of such a display compared to the more familiar electrochromic ones is that only two leads need be provided to the cell rather than the multiple leads and complicated electrical addressing required for a large screen or multi-character display. While the contrast ratio for $HVBr$ on $GaAs$ is not very good, in principle a wide band gap semiconductor ($E_g > 3$ eV), which would appear white and would be addressed with an ultraviolet beam could be employed. For a display involving rapid scanning, a system with a faster response time is also required. Similar concepts involving semiconductors and metal depositions for photoimaging have been reported (24, 27).

ACKNOWLEDGMENT

The support of this research by the Office of Naval Research, which is a joint project with Professor A.B.P. Lever of York University, and the National Science Foundation is gratefully acknowledged.

REFERENCES

- (1) R. Memming, in "Electroanalytical Chemistry," A.J. Bard, ed., Marcel Dekker, New York, 1979, Vol. 11, pp. 1-84.
- (2) A. J. Nozik, Ann. Rev. Phys. Chem., 29, 189 (1978).
- (3) H. Gerischer, J. Electroanal. Chem., 58, 263 (1979).
- (4) A. J. Bard, J. Photochem, 10, 59 (1979).
- (5) D. Laser and A. J. Bard, J. Electrochem. Soc., 123, 1027 (1976).
- (6) T. Inoue, T. Watanabe, A. Fujishima, K. Honda, and K. Kohayakawa, J. Electrochem. Soc., 124, 719 (1977).
- (7) A. B. Ellis, J. M. Bolts, S. W. Kaiser and M. S. Wrighton, J. Am. Chem. Soc., 99, 2848 (1977).
- (8) R. Memming, in Proceedings of Conference on Electrochemistry and Physics of Semiconductor-Liquid Interface under Illumination, Airlie, Va., A. Heller, ed., pp. 38-48.
- (9) J. M. Bolts, A. B. Ellis, K. D. Legg and M. S. Wrighton, J. Am. Chem. Soc., 99, 4826 (1977).
- (10) G. Hodes, J. Manassen and D. Cahen, Nature, 261, 403 (1976).
- (11) J. Manassen, G. Hodes and D. Cahen, J. Electrochem. Soc., 124, 533 (1977).
- (12) R. N. Noufi, P. A. Kohl and A. J. Bard, J. Electrochem. Soc., 125, 375 (1978).
- (13) P. A. Kohl and A. J. Bard, J. Electrochem. Soc., 126, 59, 603 (1979).
- (14) B. A. Parkinson, A. Heller and B. Miller, J. Electrochem. Soc., 126, 954 (1979).
- (15) R. Memming, J. Electrochem. Soc., 125, 117 (1978).
- (16) H. Yoneyama, H. Sakamoto and H. Tamura, Electrochim. Acta, 20, 341 (1975).

- (17) R. E. Malpas, K. Itaya and A. J. Bard, *J. Am. Chem. Soc.*, 101, 2535 (1979).
- (18) M. Tomkiewicz and J. M. Woodall, *J. Electrochem. Soc.*, 124, 1436 (1977).
- (19) P. A. Kohl and A. J. Bard, *J. Electrochem. Soc.*, 126, 59 (1979).
- (20) C. J. Schoot, J. J. Ponjee, H. T. Van Dam, R. A. Van Doorn and P. T. Bolneijn, *Appl. Phys. Lett.*, 23, 64 (1973).
- (21) R. J. Jasinski, *J. Electrochem. Soc.*, 124, 637 (1977).
- (22) J. Bruinind and C.G.A. Kregting, *J. Electrochem. Soc.*, 125, 1397 (1978).
- (23) J. D. Luttmmer and A. J. Bard, *J. Electrochem. Soc.*, 126, 414 (1979).
- (24) T. Inoue, A. Fujishima and K. Honda, *Chem. Lett.*, 11, 1197 (1978).
- (25) M. Yamana, *Appl. Physics Lett.*, 29, 571 (1976).
- (26) Fu-Ren F. Fan and A. J. Bard, *J. Am. Chem. Soc.* (submitted).
- (27) e.g., G. L. McLeod, *Photogr. Sci. Eng.*, 13, 93 (1969).

FIGURE CAPTIONS

- Fig. 1 Cyclic voltammograms recorded with p-GaAs at 100 mV/sec with aqueous solution containing 0.01 M H₂VO₄ and 0.2 M KBr (a) in the dark; (b) under illumination; (c) cyclic voltammogram recorded with the same solution on a Pt disk electrode (100 mV/sec); (d) cyclic voltammogram recorded with p-GaAs in solution containing only 0.2 M KBr. Light source, 450 W Xe lamp.
- Fig. 2 Current-time transients in potential step experiments on p-GaAs in solution containing 0.01 M H₂VO₄ and 0.2 M KBr (a) potential stepped between -0.5 and +0.1 V under constant illumination; (b) the potential held at -0.35 V vs. S.C.E. under chopped illumination. Light source, 450 W Xe lamp.
- Fig. 3 Consecutive cyclic voltammograms at irradiated p-GaP solution containing 0.01 M H₂VO₄ and 0.2 M KBr. Scan rate, 100 mV/sec. Light source, 450 W Xe lamp.
- Fig. 4 Scan rate v dependence of the peak cathodic photocurrent at irradiated p-GaAs in a solution containing 0.1 M H₂VO₄ and 0.2 M KBr. Light source, 450 W Xe lamp.
- Fig. 5 Cyclic voltammograms at p-GaAs in solution of Fig. 4 with different relative light intensities. Light source, 450 W Xe lamp.
- Fig. 6 Schematic description of the H₂VO₄-based photoelectrochemical cell operating (a) under illumination (photocharge); (b) in the dark (discharge); (c) relative energy levels and potentials at the counter electrode and at the p-GaAs, required for operation of the cell shown in (a) and (b).

- Fig. 7 (A) Open circuit potentials and (B) short circuit current under chopped illumination for the cells (a) p-GaAs/HVBr/HVBr₂,KBr/Cu; (b) p-GaAs/HVBr/HVBr₂,KBr/Nb₂O₅; (c) p-GaAs/HVBr/HVBr₂,KBr/Ni. Light source, 450 W Xe lamp.
- Fig. 8 Initial short circuit photocurrents for the three cells described in Fig. 7 as a function of light intensity (He-Ne laser).
- Fig. 9 Schematic description of the energy levels of the HVBr₂ based photoelectrochemical cells in the light at (a) short circuit, no HVBr film on p-GaAs initially and (b) open circuit, no HVBr film on p-GaAs initially. In the dark at (c) short circuit, with HVBr film on p-GaAs and (d) open circuit, with HVBr film on p-GaAs. E_c = conduction band edge of p-GaAs; E_f = Fermic energy of p-GaAs; E_v = valence band edge of p-GaAs; s.s. = surface state; E_v^0 = energy corresponding to the redox potential of heptyl viologen couple; E_c^0 = energy corresponding to the redox potential of the counter electrode; V_{ph} = open circuit voltage in the light; V_{dk} = open circuit voltage in the dark; V_{on} = onset potential of photocurrent.
- Fig. 10 Schematic description of a photoelectrochromic display device based on HVBr₂ reduction on p-GaAs electrode.

FIG. 1


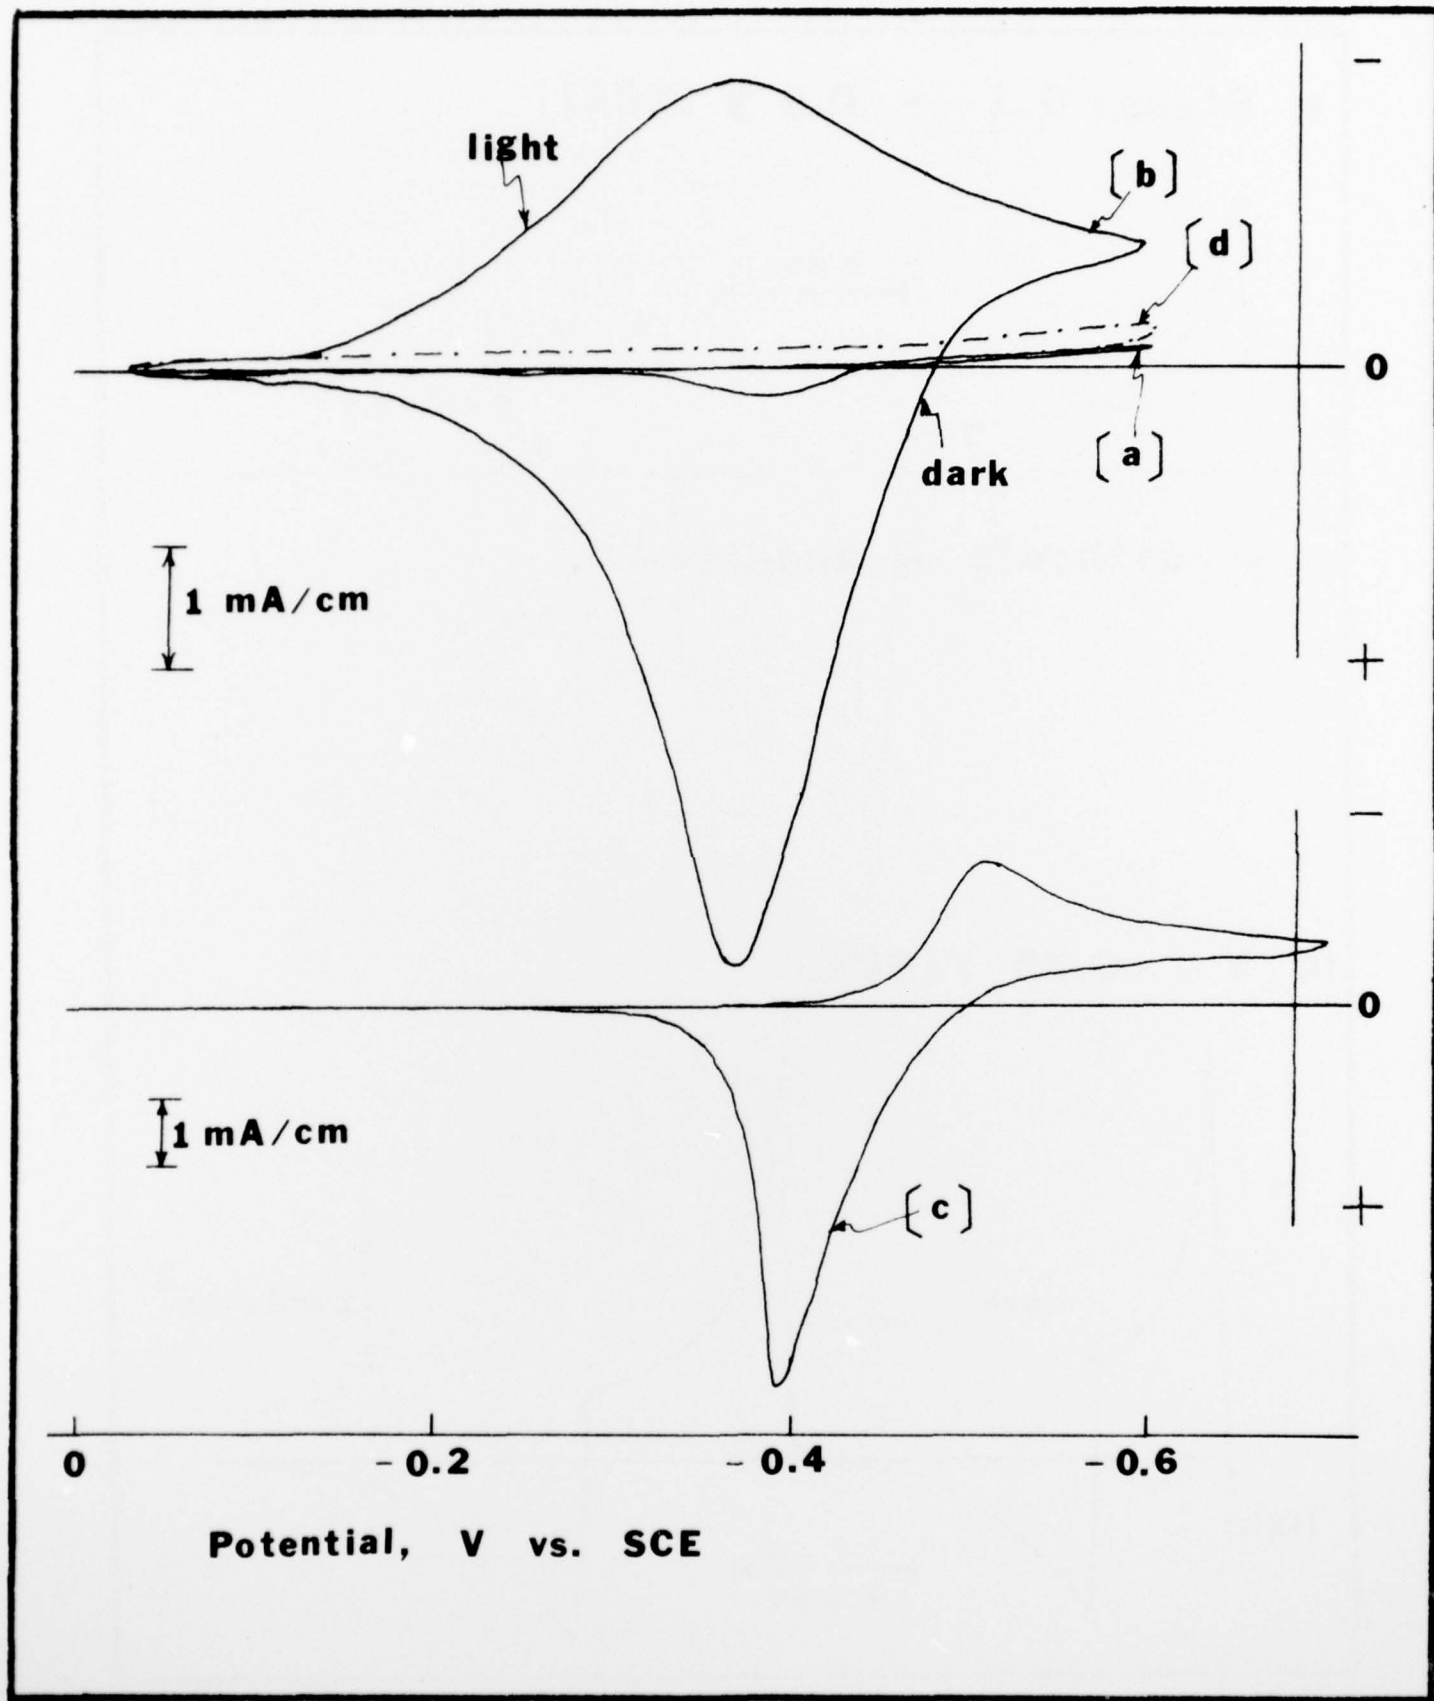


Fig 2

a. Steps: $0.1 \leftrightarrow -0.5$ V (SCE)

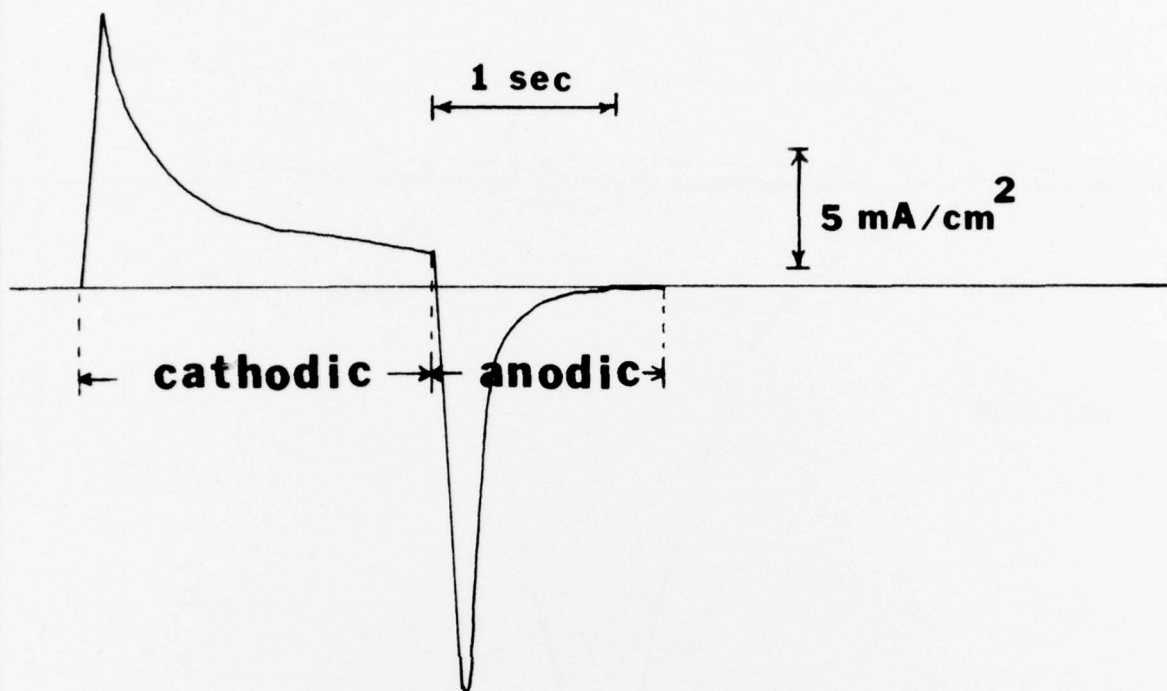

b. $V = -0.35$ V (SCE)

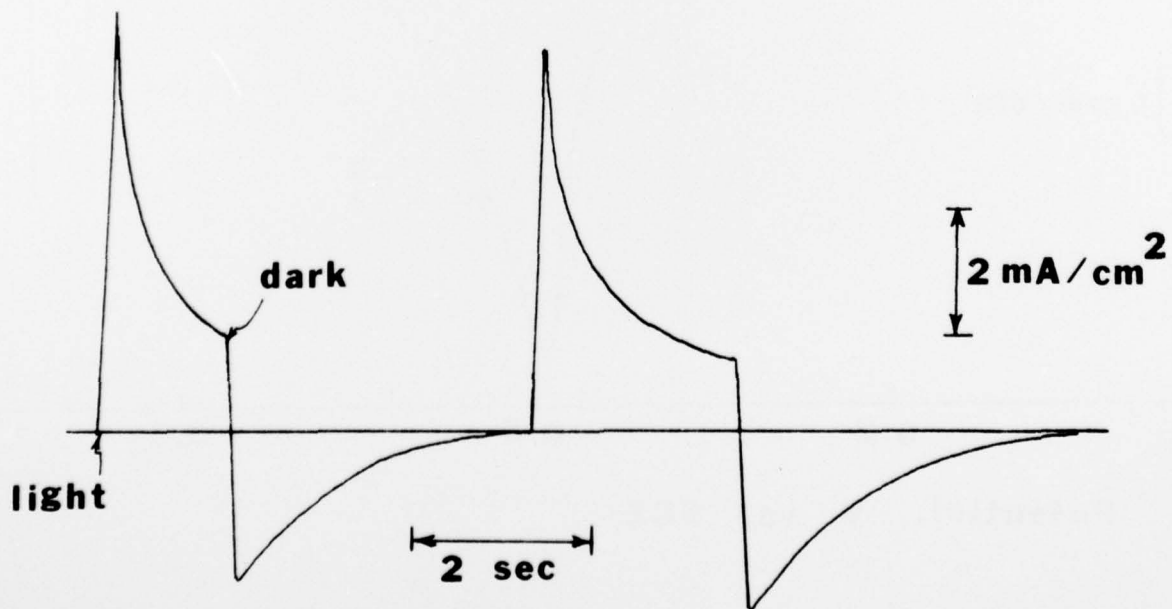


Fig. 3

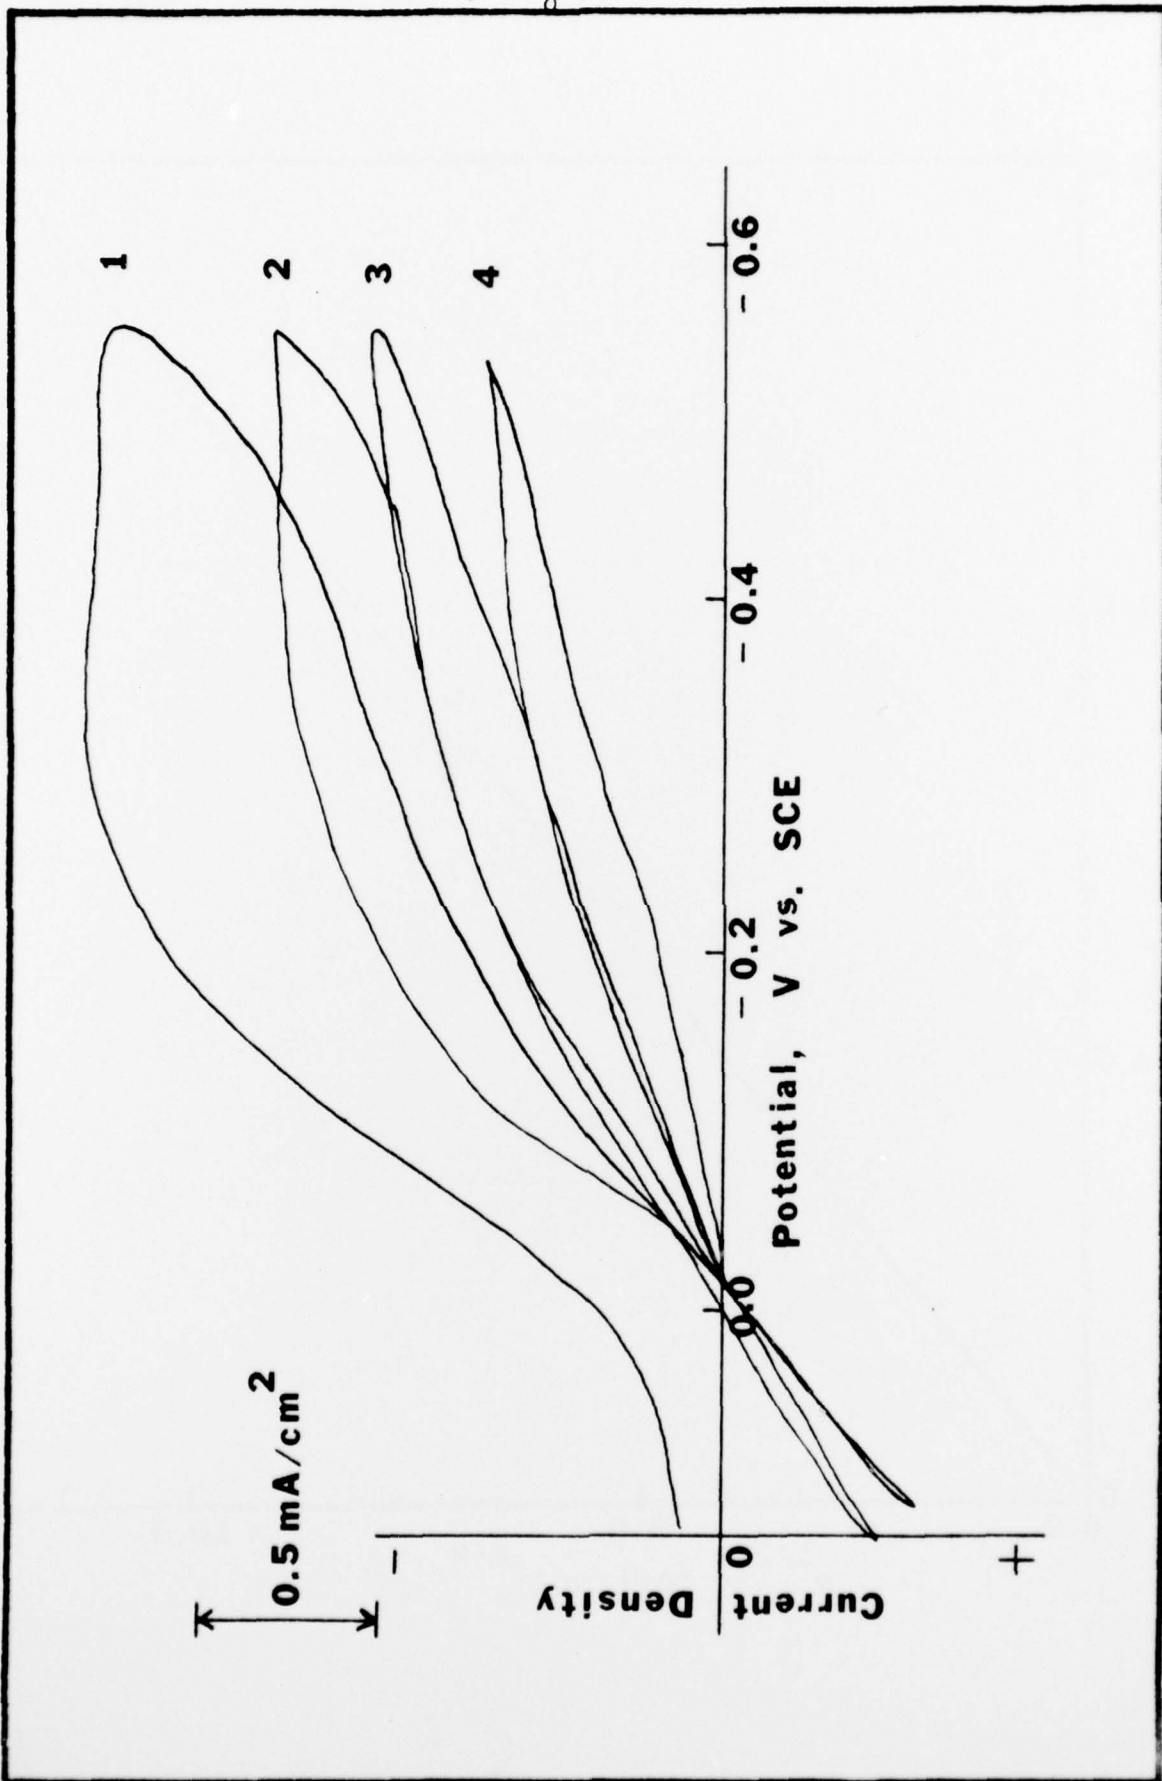


Fig. 4




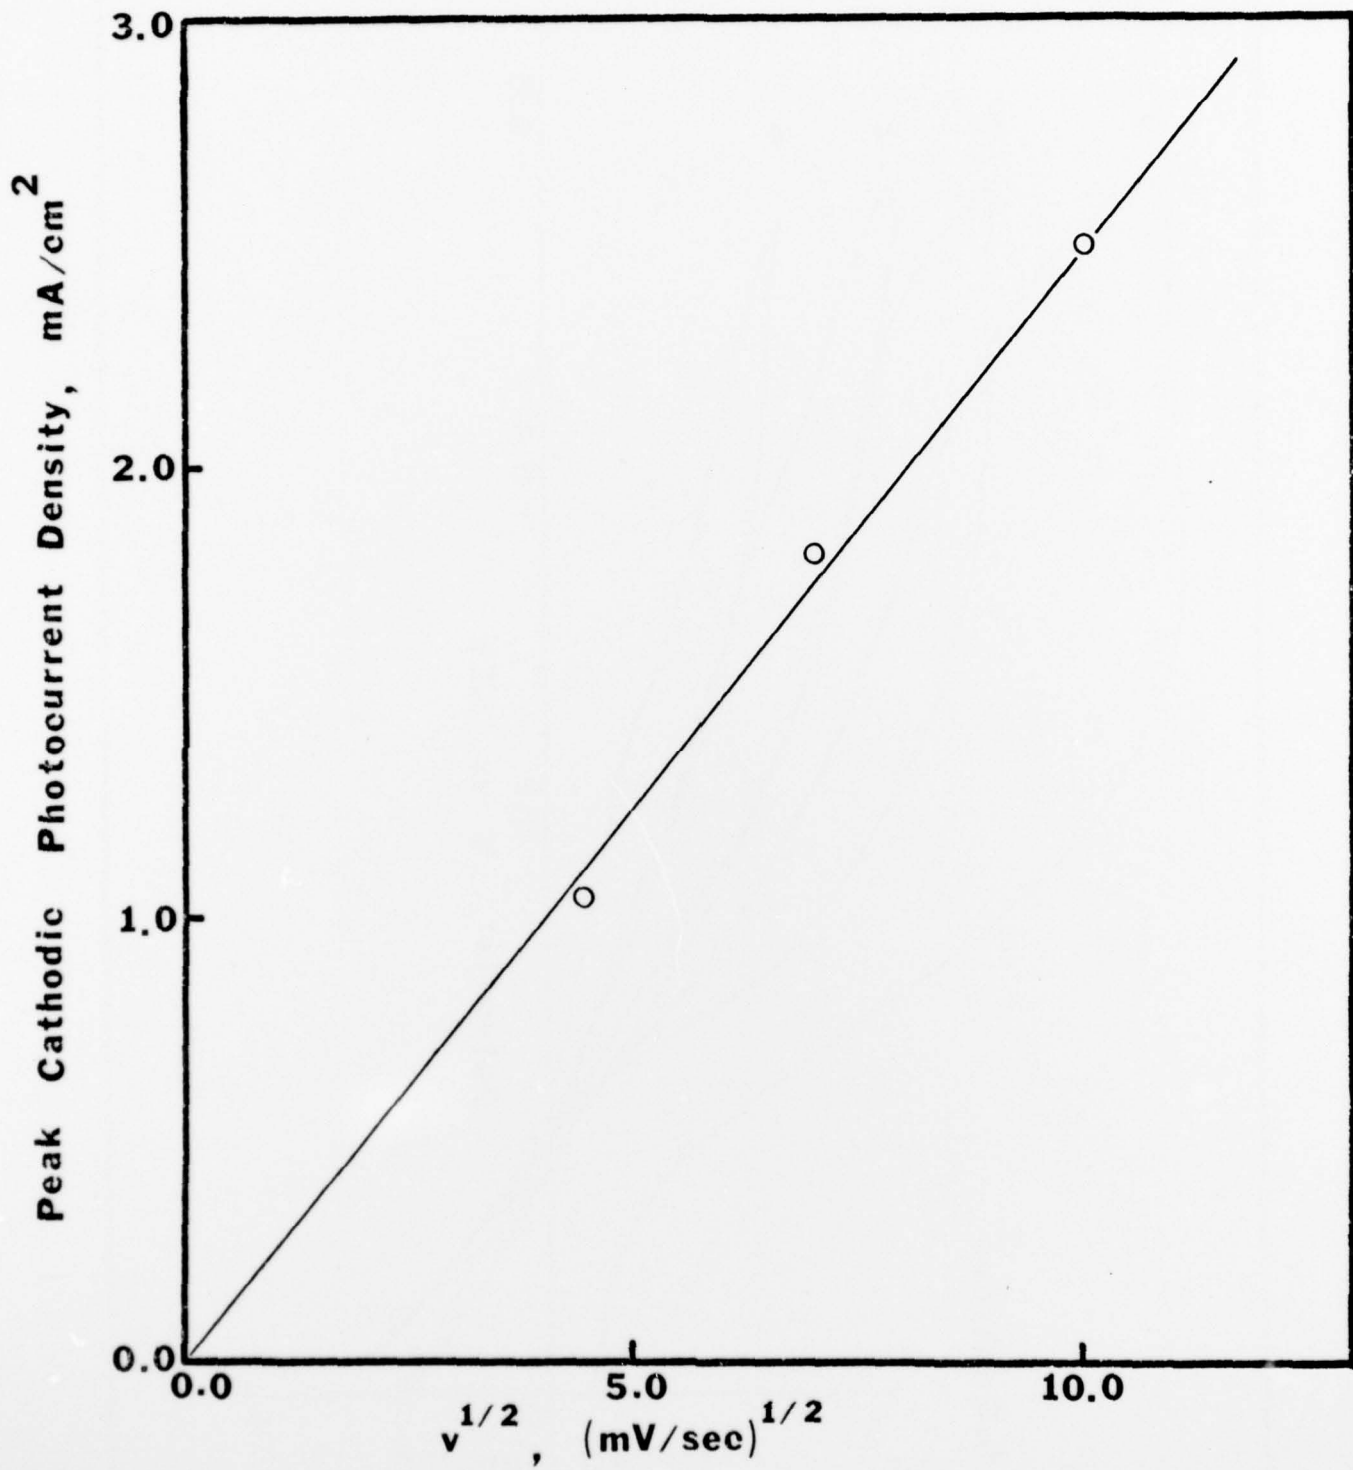


Fig 5

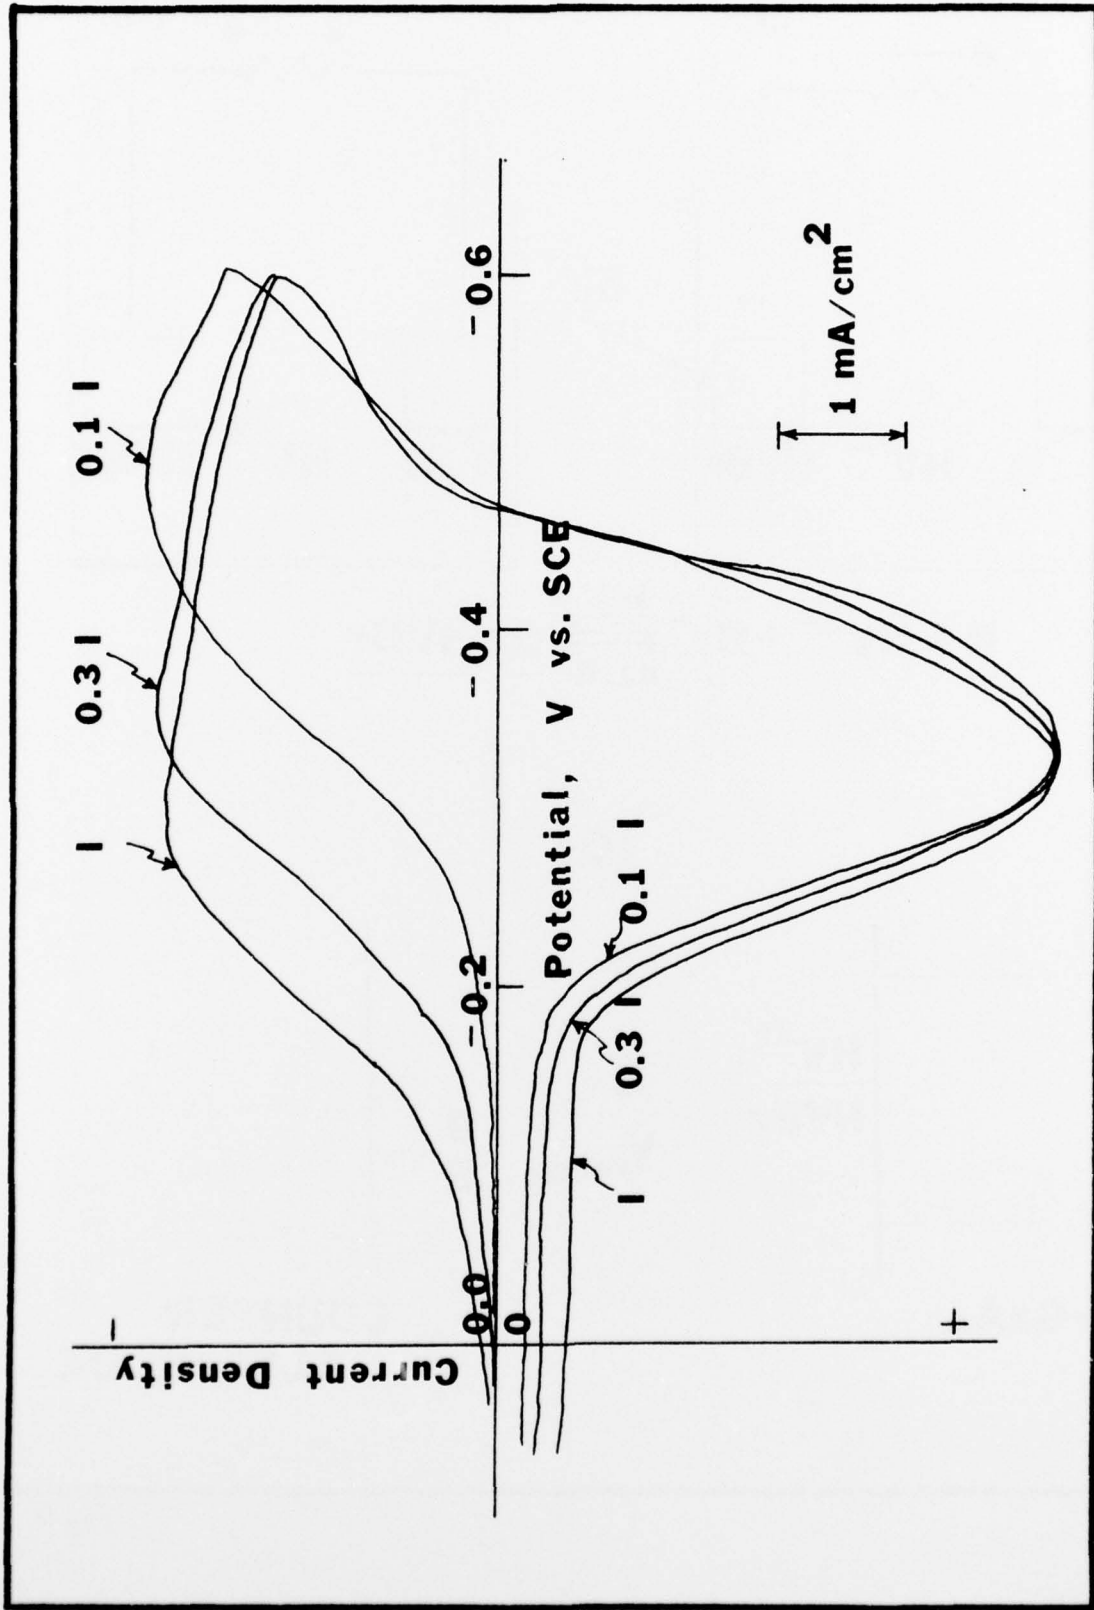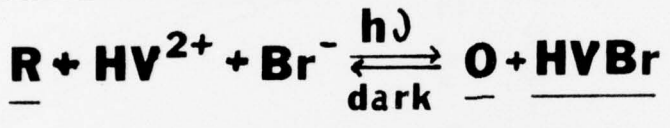

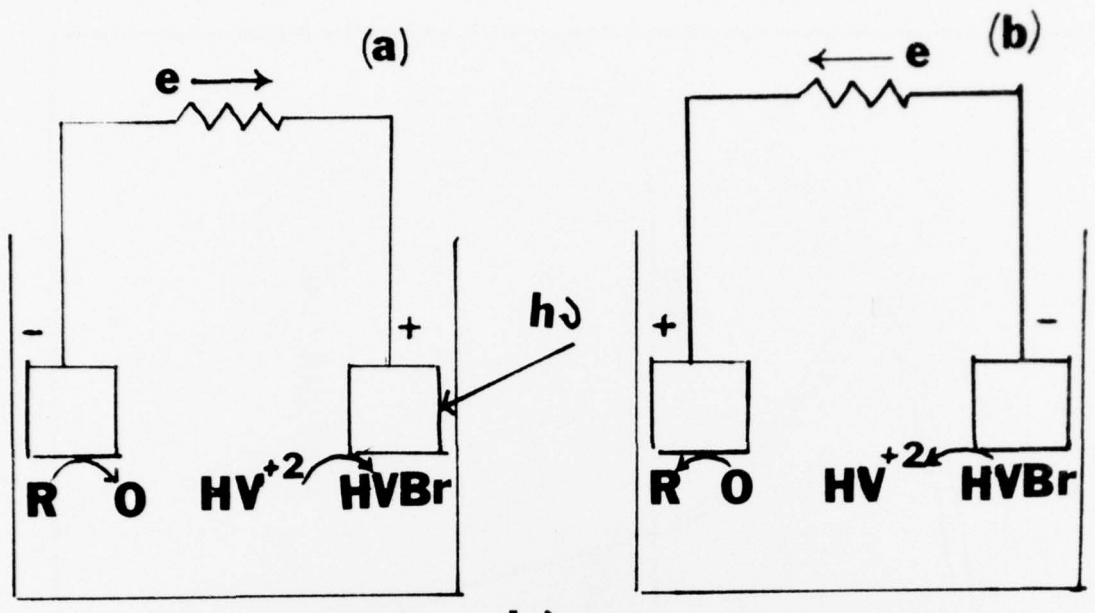

(C)

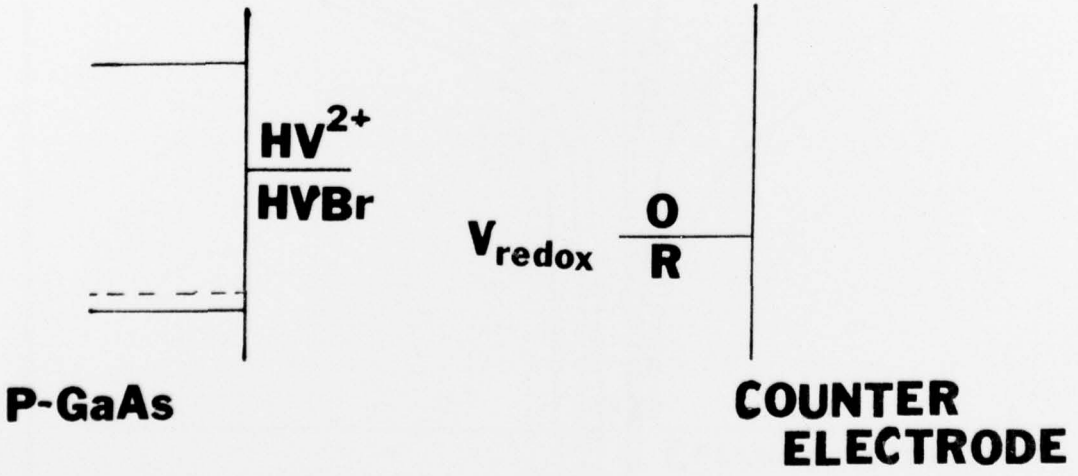


Fig 6

Fig 7

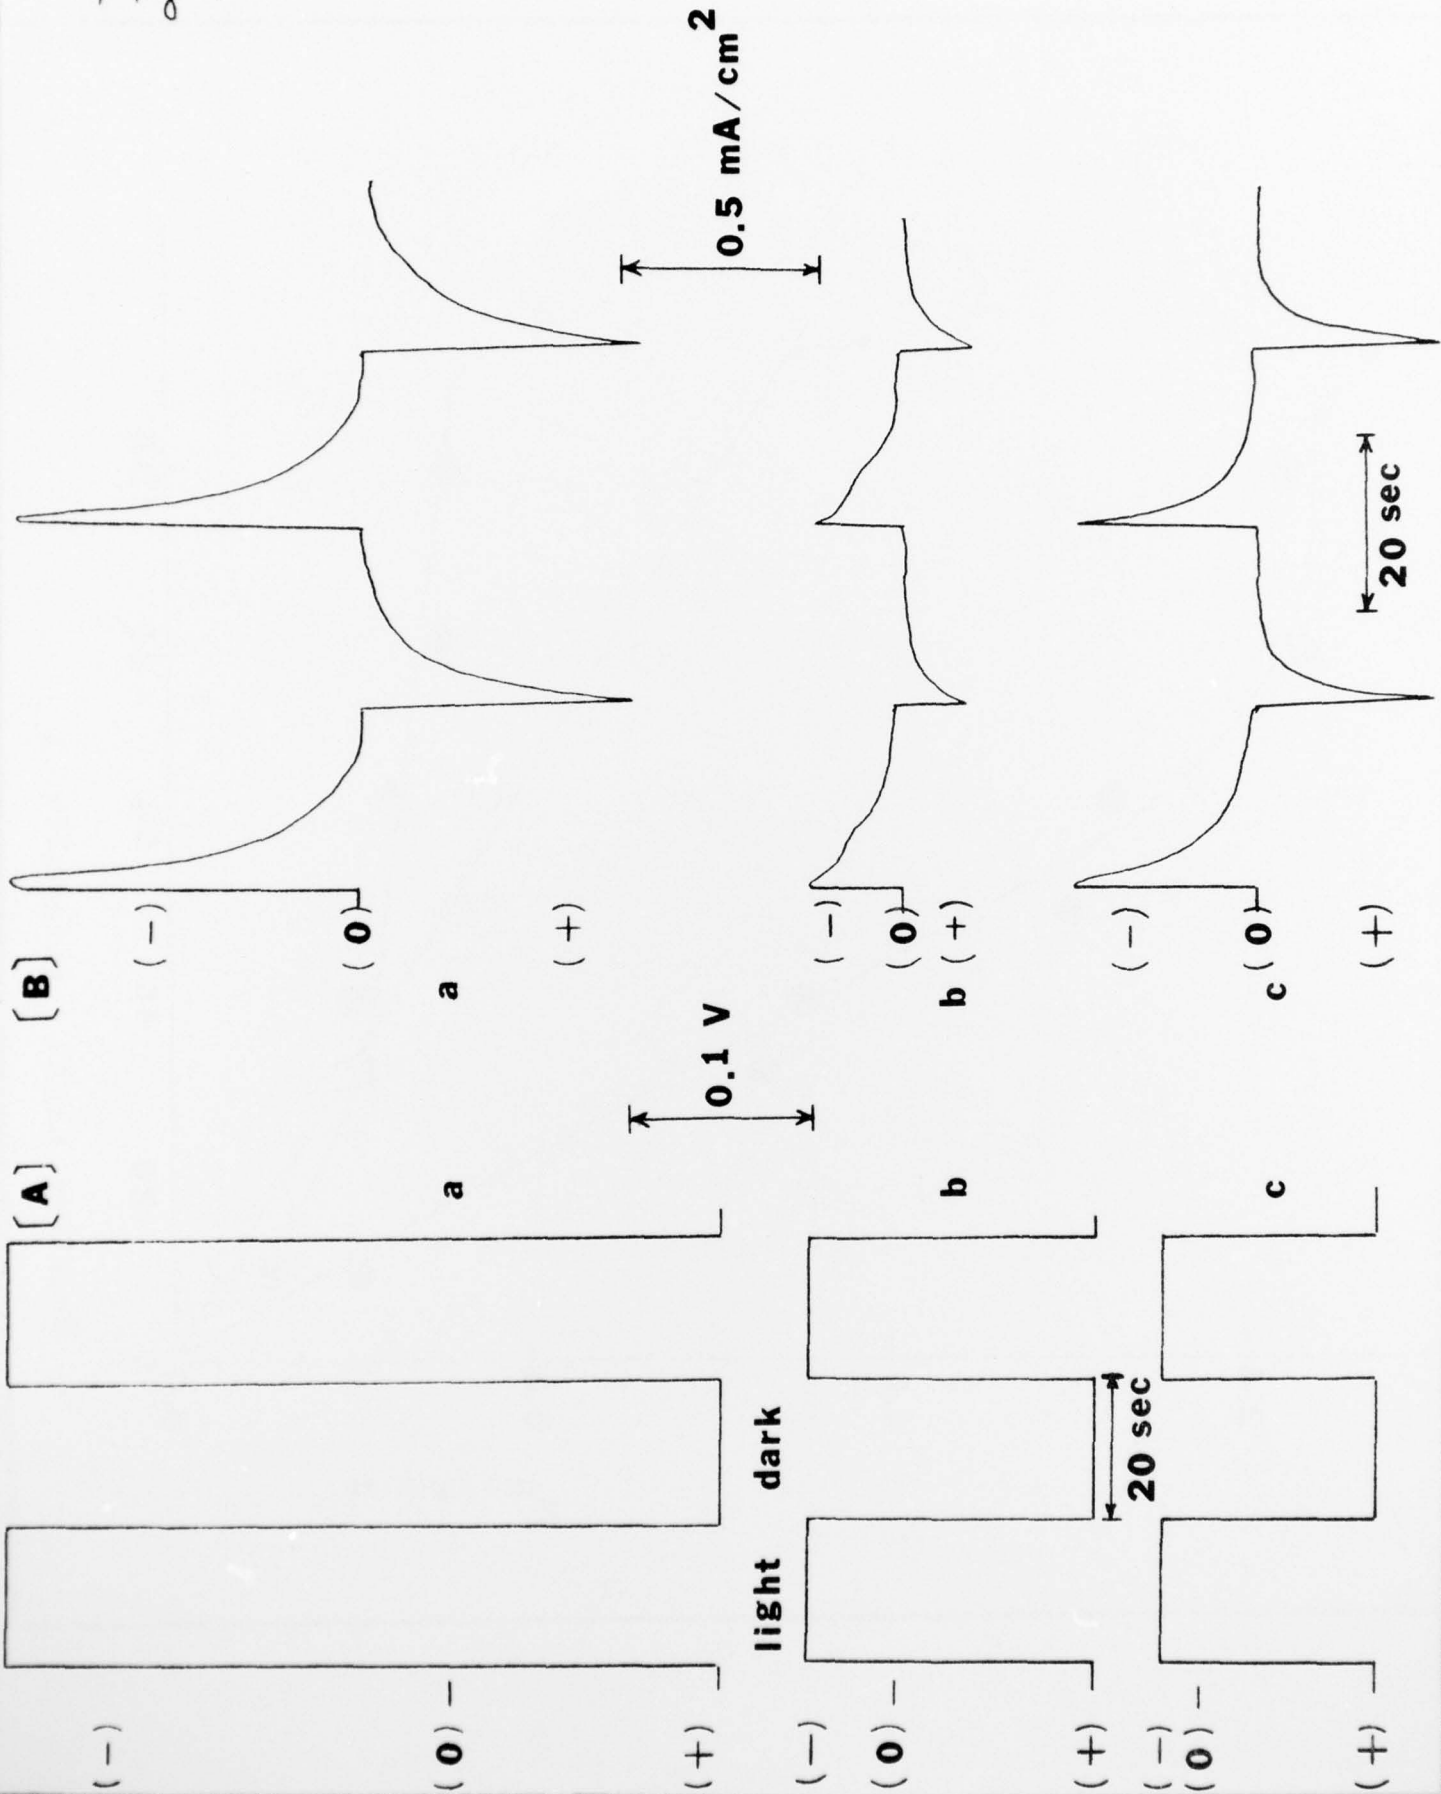


Fig 8

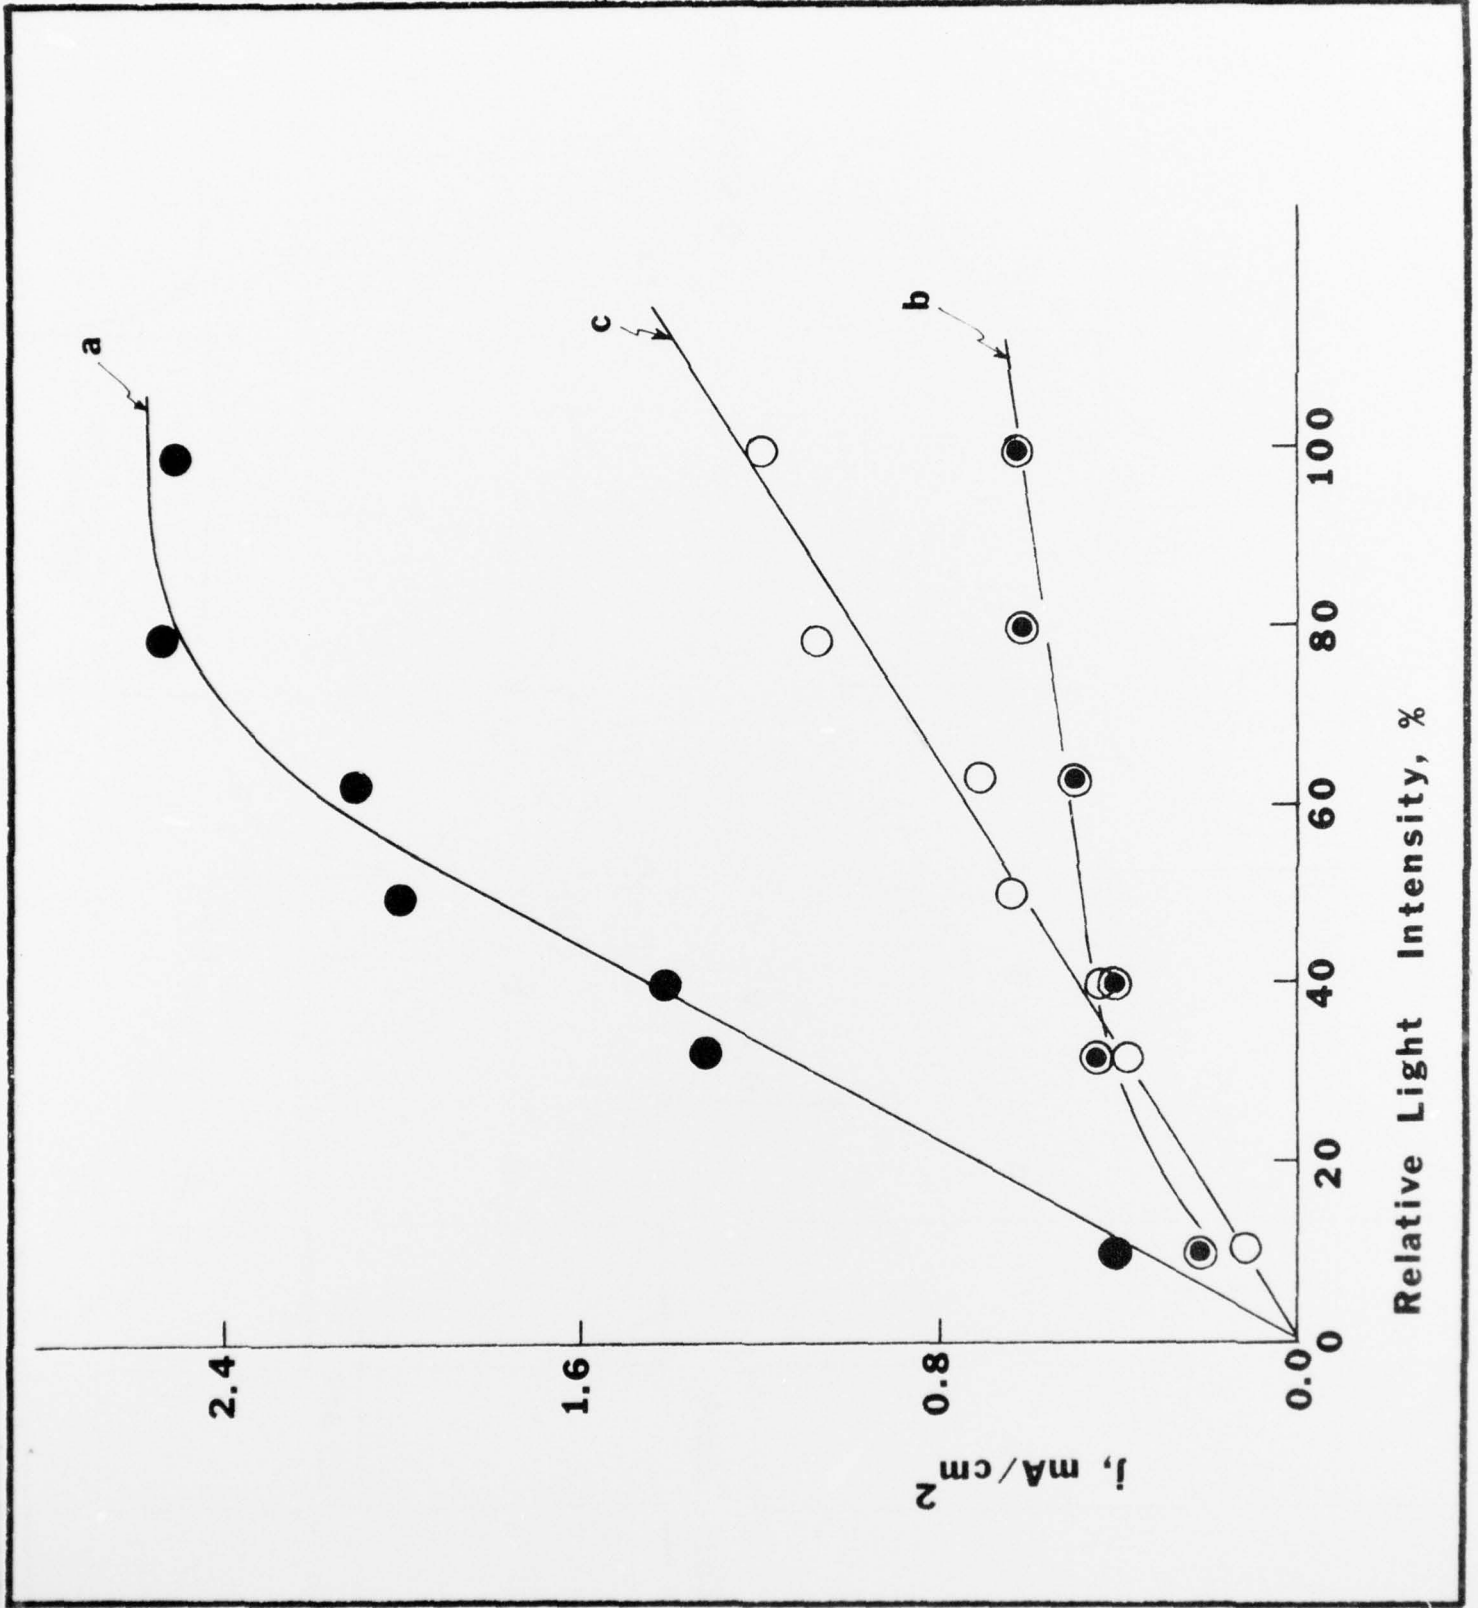


Fig 9

p-GaAs Electrolyte Counter-electrode


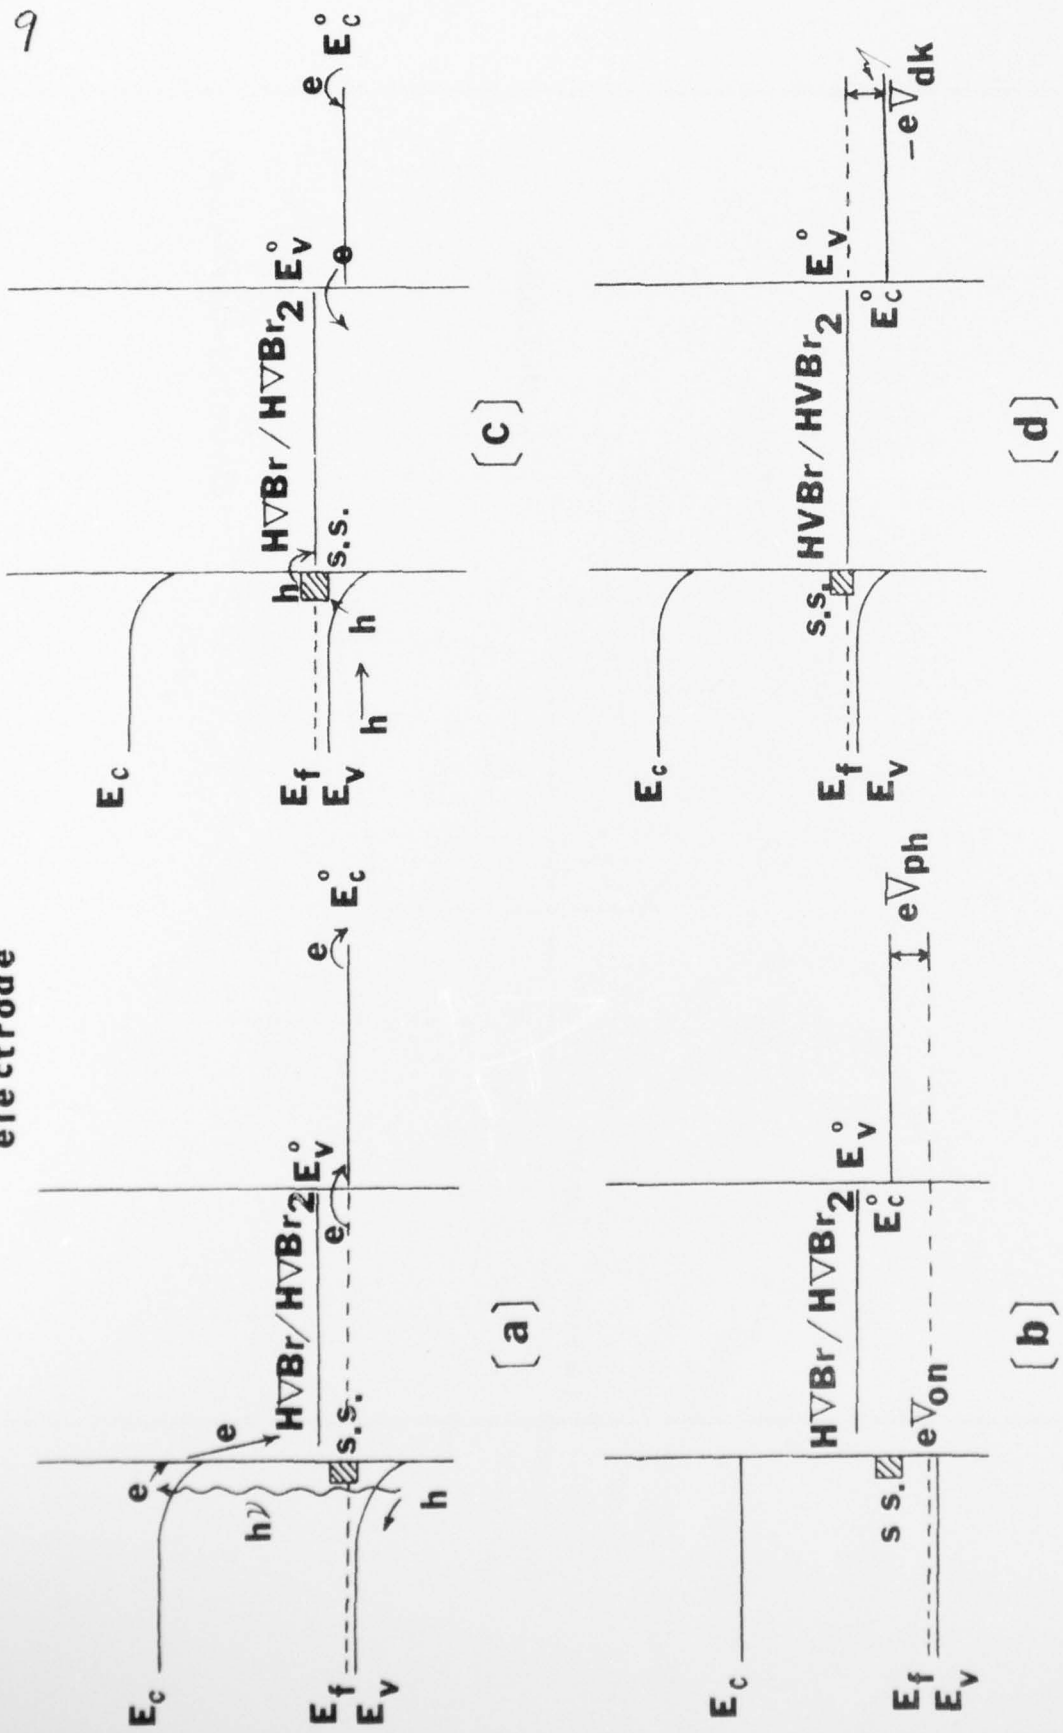


Fig 10

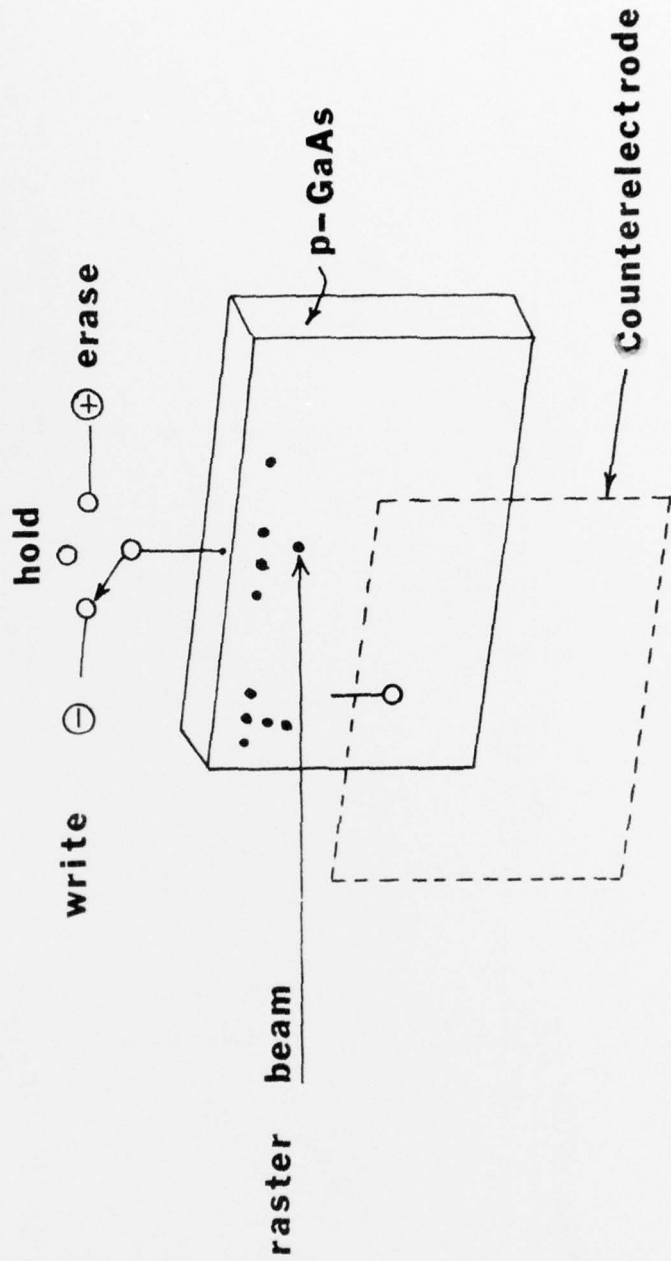

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Office of Naval Research 800 North Quincy Street Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. George Sandoz	1	U.S. Army Research Office P.O. Box 1211 Research Triangle Park, N.C. 27709 Attn: CRD-AA-IP	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Mr. Joe McCartney	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Weapons Center China Lake, California 93555 Attn: Dr. A. B. Amster Chemistry Division	1
ONR Area Office One Hallidie Plaza, Suite 601 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Naval Civil Engineering Laboratory Port Hueneme, California 93401 Attn: Dr. R. W. Drisko	1
ONR Branch Office Building 114, Section D 666 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Professor K. E. Woehler Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Washington, D.C. 20390 Attn: Code 6100	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (R,E&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research 800 N. Quincy Street Arlington, Virginia 22217 Attn: Dr. Richard S. Miller	1
Commander, Naval Air Systems Command Department of the Navy Washington, D.C. 20360 Attn: Code 310C (H. Rosenwasser)	1	Naval Ship Research and Development Center Annapolis, Maryland 21401 Attn: Dr. G. Bosmajian Applied Chemistry Division	1
		Naval Ocean Systems Center San Diego, California 91232 Attn: Dr. S. Yamamoto, Marine Sciences Division	1

Encl 1

TECHNICAL REPORT DISTRIBUTION LIST, 359


	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. Paul Delahay New York University Department of Chemistry New York, New York 10003	1	Library P. R. Mallory and Company, Inc. Northwest Industrial Park Burlington, Massachusetts 01803	1
Dr. R. A. Osteryoung Colorado State University Department of Chemistry Fort Collins, Colorado 80521	1	Dr. P. J. Hendra University of Southampton Department of Chemistry Southampton SO9 5NH United Kingdom	1
Dr. E. Yeager Case Western Reserve University Department of Chemistry Cleveland, Ohio 41106	1	Dr. Sam Perone Purdue University Department of Chemistry West Lafayette, Indiana 47907	1
Dr. D. N. Bennion University of California Chemical Engineering Department Los Angeles, California 90024	1	Dr. Royce W. Murray University of North Carolina Department of Chemistry Chapel Hill, North Carolina 27514	1
Dr. R. A. Marcus California Institute of Technology Department of Chemistry Pasadena, California 91125	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Technical Library	1
Dr. J. J. Auburn Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. J. H. Ambrus The Electrochemistry Branch Materials Division, Research & Technology Department Naval Surface Weapons Center White Oak Laboratory Silver Spring, Maryland 20910	1
Dr. Adam Heller Bell Telephone Laboratories Murray Hill, New Jersey 07974	1	Dr. G. Goodman Globe-Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. T. Katan Lockheed Missiles & Space Co, Inc. P.O. Box 504 Sunnyvale, California 94088	1	Dr. J. Boechler Electrochimica Corporation Attention: Technical Library 2485 Charleston Road Mountain View, California 94040	1
Dr. Joseph Singer, Code 302-1 NASA-Lewis 21000 Brookpark Road Cleveland, Ohio 44135	1	Dr. P. P. Schmidt Oakland University Department of Chemistry Rochester, Michigan 48063	1
Dr. B. Brummer EIC Incorporated Five Lee Street Cambridge, Massachusetts 02139	1		

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No.</u> <u>Copies</u>
Dr. H. Richtol Chemistry Department Rensselaer Polytechnic Institute Troy, New York 12181	1
Dr. A. B. Ellis Chemistry Department University of Wisconsin Madison, Wisconsin 53706	1
Dr. M. Wrighton Chemistry Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1
Larry E. Plew Naval Weapons Support Center Code 3073, Building 2906 Crane, Indiana 47522	1
S. Ruby DOE (STOR) 600 E Street Washington, D.C. 20545	1
Dr. Aaron Wold Brown University Department of Chemistry Providence, Rhode Island 02192	1
Dr. R. C. Chudacek McGraw-Edison Company Edison Battery Division Post Office Box 28 Bloomfield, New Jersey 07003	1
Dr. A. J. Bard University of Texas Department of Chemistry Austin, Texas 78712	1
Dr. M. M. Nicholson Electronics Research Center Rockwell International 3370 Miraloma Avenue Anaheim, California 92803	1
Dr. M. G. Sceats University of Rochester Department of Chemistry Rochester, New York 14627	1



(a)

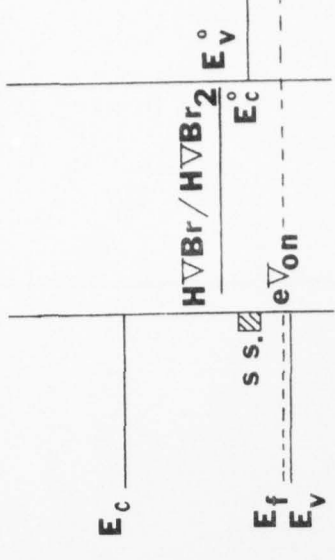

(b)