

AD-A078 555

QUARTERMASTER RESEARCH AND DEVELOPMENT LABS PHILADEL--ETC F/G 18/8
OPERATION SNAPPER. TEST CONDUCTED AS PART OF EXERCISE DESERT RO--ETC(U)
MAY 53 J M DAVIES


UNCLASSIFIED

1 OF 1

AD
AD 78555

NL



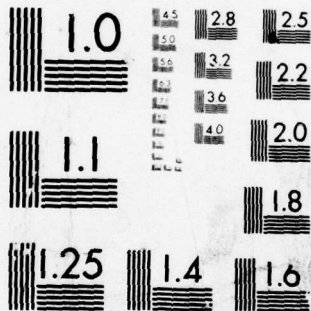

MICROCOPY RESOLUTION TEST CHART
 NATIONAL BUREAU OF STANDARDS-1963-A

PHOTOGRAPH THIS SHEET

ADA 078555

DTIC ACCESSION NUMBER



LEVEL



INVENTORY

Operation Snapper. Test conducted as part of Exercise Desert Rock IV. May - June 1952. The Susceptibility to Damage and the Protection Afforded By Quartermaster Items. I. Clothing II. CI. --- III. P. --- IV. P. ---


DISTRIBUTION STATEMENT A

Approved for public release; Distribution Unlimited

DISTRIBUTION STATEMENT

ACCESSION FOR	
NTIS	GRA&I <input checked="" type="checkbox"/>
DTIC	TAB <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
Per Hr. on file	
BY	
DISTRIBUTION /	
AVAILABILITY CODES	
DIST	AVAIL AND/OR SPECIAL
A	

DISTRIBUTION STAMP

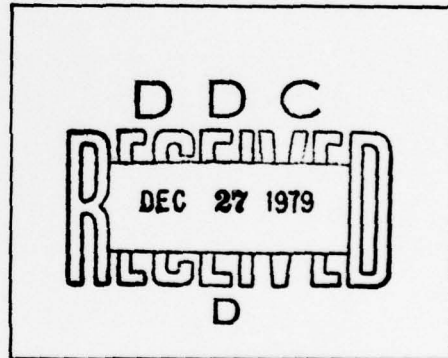

DATE ACCESSIONED

79 12 18 361

DATE RECEIVED IN DTIC

PHOTOGRAPH THIS SHEET AND RETURN TO DTIC-DDA-2

DR4

27407
A4732
C17

ADA 078555

~~SECURITY INFORMATION~~

OPERATION SNAPPER. TEST CONDUCTED AS PART OF
EXERCISE DESERT ROCK IV.
MAY-JUNE 1952

OFFICE OF THE
SECRETARY OF DEFENSE
WASHINGTON, D.C.
MAY 19 1953

#9

THE SUSCEPTIBILITY TO DAMAGE AND THE PROTECTION
AFFORDED BY QUARTERMASTER ITEMS

- I. Clothing
- II. Clothing Fabrics
- III. Protective Cream
- IV. Packaging

OWN ✓
DOC ✓
S
D

Statement A
Approved for public release;
Distribution unlimited.

By

JOHN M. DAVIES
Philadelphia QM
Research and Development
Laboratories

Classification (Cancelled) ~~(Classified)~~ **DI/DNA** **EX**
 By Authority of **DI/DNA**
 By **[Signature]** Date **10 Jul 1977**
 w/enclosure **DOC**

NO RESTRICTED DATA OR FORMERLY RESTRICTED DATA.
 ERDA HAS NO OBJECTION TO ITS DECLASSIFICATION.
 COORDINATION REQUIRED WITH **DNA**
 REVIEWED BY **[Signature]** DATE **11/31/76**

26 May 1953



~~18-002668~~

UNCLASSIFIED

SECURITY INFORMATION

THE-340

[REDACTED]
UNCLASSIFIED

This document consists
of 77 plus 4 pages
(counting preliminary
pages)

No. 17 of 30 copies.

[REDACTED]

This document contains restricted data as de-
fined in the Atomic Energy Act of 1946. Its
transmittal or the disclosure of its contents
in any manner to an unauthorized person is pro-
hibited.

This document contains information affecting
the national defense of the United States
within the meaning of the Espionage Laws,
Title 18 U.S.C. Sections 793 and 794. The
transmission or the revelation of its con-
tents in any manner to an unauthorized person
is prohibited by law.

[REDACTED]
UNCLASSIFIED

[REDACTED]
UNCLASSIFIED

DTL 007448

ACKNOWLEDGMENTS

These tests were performed as part of Exercise Desert Rock IV, carried out by Sixth Army under direction of the Chief of Army Field Forces. We wish to thank the Chief of Army Field Forces for allowing Quartermaster Research & Development to take part in the test and the Test Director, Gen. H. P. Storke, and his staff, for assistance in conducting the tests. Major D. E. Kieffer was particularly helpful. Lt. Edwards of the Signal Corps Photo Detachment took the photographs at the site.

Lt. Col. D. C. Hughes of the Quartermaster Board, Ft. Lee, Va., was the Project Officer at the Test Site assisted by Major Howard James, Lieut. Frank Simpson and Pfc. Nannig. Lieut. Simpson was especially helpful in locating shipments and setting up samples for exposure in Shot 6 before the others arrived.

A considerable amount of help was given by members of the Philadelphia QM Research and Development Laboratories. The dummies, clothing and many of the fabric samples were obtained by Mr. Elliott A. Snell of the Engineering Test Division. Other materials were furnished by Mr. Frank J. Rizzo of the Dyeing and Finishing Branch of the Textile Division and by Mr. F. Tartaglia of the Clothing Division. The temperature indicators were furnished by Dr. J. D. Loconti of the Pioneering Research Division. The preparation of samples and indicators was largely handled by Mr. Emery Utterback of the Pioneering Research Division, assisted by Miss Norma Weber of the Engineering Test Division. Reflectance and transmittance data were obtained by Mr. Samuel P. Cohen and his staff in the Pioneering Research Division. A number of photographs were taken by Mr. John Salmon of the Photography Division of the Philadelphia Quartermaster Depot.

- iii -

UNCLASSIFIED [REDACTED]

[REDACTED]
ACT - 1946

UNCLASSIFIED

CONTENTS

SUMMARY ix

CHAPTER 1 OBJECTIVES AND GENERAL PLAN. 1

 1.1 Objectives. 1

 1.2 History and General Plan 1

CHAPTER 2 OPERATION AND GENERAL PROCEDURE 3

 2.1 General. 3

 2.2 Thermal Intensities. 3

 2.3 Weather. 3

 2.4 Reflectance and Transmittance of Materials 4

 2.5 Temperature Indicators. 4

CHAPTER 3 CLOTHING ON DUMMIES 9

 3.1 Procedure and Materials 9

 3.2 Damage to Clothing 9

 3.2.1 Hot Wet Ensemble 10

 3.2.2 Hot Dry Ensemble 10

 3.2.3 Temperate. 11

 3.2.4 Cold Wet 12

 3.2.5 Cold Dry 12

 3.2.6 Summary 13

 3.3 Protective Value of Clothing. 14

 3.3.1 Hot Wet 15

 3.3.2 Hot Dry 15

 3.3.3 Temperature 15

 3.3.4 Cold Wet 15

 3.3.5 Cold Dry 15

 3.3.6 Summary 15

CHAPTER 4 FABRICS ON PANELS 46

 4.1 Procedure 46

 4.1.2 Method of Mounting. 46

 4.2 Fabrics. 46

 4.3 Damage to Fabrics 46

 4.3.1 Photographs 46

 4.3.2 Damage Code 47

 4.3.3 Damage at Low Intensities 48

 4.3.4 Damage at 10 to 13 Langleys. 48

 4.3.4.1 Fabrics Equivalent to Clothing Ensembles. 48

 4.3.4.2 Reflectance 48

 4.3.4.3 Backing and Under Layers. 48

 4.3.4.4 Material 49

 4.3.5 Summary 49

 4.4 Protective Value of Fabrics 50

 4.4.1 Fabrics Equivalent to Clothing Ensembles 50

 4.4.2 Effect of Reflectance. 51

UNCLASSIFIED

APR 1980


[REDACTED]
UNCLASSIFIED

CONTENTS (cont'd)

4.4.3	Transmittance of Under Layers	51
4.4.4	Blends of Fibers.	52
4.4.5	Orlon	52
4.4.6	Aluminized Fabrics	52
4.4.7	Order of Layers and Location of Spacing	52
4.4.8	Spacing.	53
4.4.9	Summary.	53
CHAPTER 5	PROTECTIVE CREAM.	72
5.1	General	72
5.2	Samples	72
5.3	Damage to the Cream	72
5.4	Protective Value	73
CHAPTER 6	PACKAGING	75
6.1	General	75
6.2	Samples and Exposure.	75

STRIPPED DATA
[REDACTED]
1946

[REDACTED]



TABLES

2.1 Calculated Intensities of Radiation 5

2.2 Temperature and Relative Humidity. All data at the Control Point except for H Hour; H Hour result calculated for shot area. 5

3.1 Clothing Ensembles. Fabric layers are in order, first layer exposed, last layer next to dummy. 17-19

3.2 Reflectance & Transmittance of Outer Layers of Clothing Fabrics Averages for Visible 20

3.3 Temperatures in Various Areas, Behind Clothing 21

4.1 Fabric Samples for Panel Tests. Fabrics are in order with First Layer Exposed, Last Layer next to Backing 55-59

4.2 Damage to Fabrics on Panels. Damage Code in Section 4.4 60-62

4.3 Temperatures behind Fabrics on Panels 63-67

5.1 Protection Afforded by QM Face Cream. 74

5.2 Temperature of Exposed Indicators. 74

6.1 Results of Packaging Test 76

FIGURES

2.1 Reflectance of Cotton and Orlon Fabrics and Protective Cream. Numbers refer to Table 4.1 6

2.2 Reflectance of Wool Fabrics. Numbers refer to Table 4.1 7

2.3 Transmittance of Materials. Numbers refer to Table 4.1 8

3.1 Dummies with Temperature Indicators 22

3.2 Shot 6 - 1-1/2 Miles Hot Wet 23

3.3 Shot 6 - 1-1/2 Miles Hot Dry 24

3.4 Shot 6 - 1-1/2 Miles Cold Wet 25

3.5a Shot 6 - 1-1/2 Miles Cold Dry Before Exposure. 26

3.5 Shot 6 - 1-1/2 Miles Cold Dry 27

3.6 Shot 6 - 1 Mile Hot Wet 28

3.7 Shot 6 - 1 Mile Hot Dry 29

3.8 Shot 6 - 1 Mile Temperate 30

3.9 Shot 6 - 1 Mile Cold Wet. 31

3.10 Shot 6 - 1 Mile Cold Dry. 32

3.11 Shot 8 - 1-1/2 Miles Hot Wet 33

3.12 Shot 8 - 1-1/2 Miles Hot Dry 34

3.13 Shot 8 - Before Exposure. 35

3.14 Shot 8 - 1-1/2 Miles Temperate. 36

3.15 Shot 8 - 1-1/2 Miles Cold Wet 37

3.16 Shot 8 - 1-1/2 Miles Cold Dry 38

3.17 Shot 8 - 1 Mile Hot Dry 39

3.18 Shot 8 - 1 Mile Hot Dry 40

3.19 Shot 8 - 1 Mile Temperate 41

3.20 Shot 8 - 1 Mile Cold Wet. 42

3.21 Shot 8 - 1 Mile Cold Dry. 43

3.22 Scorching of Dummies under Hot Wet and Hot Dry Ensembles, 1 Mile, Shots 6 & 8 44



UNCLASSIFIED DATA
AT
APR 1946

~~SECRET~~
UNCLASSIFIED

FIGURES (cont'd)

3.23 Scorching of Under Layers, 1 Mile, Hot Wet	
Shot 6, Hot Wet Shot 8, Cold Wet Shot 8.	45
4.1 Fabrics on Panels - Shot 6 - 1-1/2 Miles	68
4.2 Fabrics on Panels Shot 6 1 Mile	69
4.3 Fabrics on Panels Shot 8 1-1/2 Miles.	70
4.4 Fabrics on Panels Shot 8 1 Mile	71

such as hot wet, hot dry, temperate, cold wet and cold dry. The fabrics on panels included essentially the same fabric combinations and various other fabrics to study reflectance, insulation, a variety of materials, including heat treated orlon, wool and synthetic fiber blends, and arrangements, including spacing and order of layers.

Except for a few items there was little damage at 5 layers. The exceptions were the cotton nylon furfs which shredded, the fur veil which melted and the wool fabrics which scorched slightly. At 10 to 13 layers all single layers of fabrics and all outer layers of fabric combinations were badly damaged. The damage to fabrics as clothing and on panels was about the same and any difference can be accounted for on the basis of angle of incidence.

Generally the damage was less for fabrics in contact with a solid backing. High reflectance reduced the damage. Wool was more sensitive than cotton at low intensities but less sensitive at high intensities. Blends of synthetics with wool up to 15 percent were about as resistant as wool but a 30 percent blend of dacron was damaged considerably. The heat treated orlon was very resistant. In aluminized cotton was very good.

There is still some uncertainty in interpreting protection from temperature indicators and the conclusions are subject to revision. It seems, however, that the lighter ensembles, such as hot wet and hot dry, did not provide adequate protection in single layers for intensities of 10 to 13 langley. Under pockets, seams, plaits and folds, the protection was adequate at this intensity. The temperate and heavier ensembles provided adequate protection at this level. Temperatures behind fabrics on panels were higher than behind clothing, largely on account of effects of angle of incidence and drapes and spacing. White fabrics did not provide as much protection as might be expected from the resistance they offer to damage and generally not as much as dyed fabrics. Likewise the black heat treated orlon did not provide outstanding protection. The aluminized cotton was outstanding and for a corresponding weight provided more protection than any other fabric. Behind the black orlon most of this advantage was lost. The temperatures back of the camouflage shades were just slightly higher than for higher reflecting shades. There was no difference between the undyed and dyed (less back of 9 vs. screen, 25-107). Reversing the order of layers gave

~~RESTRICTED~~
~~SECRET~~

~~SECRET~~

UNCLASSIFIED

[REDACTED]

UNCLASSIFIED

SUMMARY

Clothing on dummies and fabrics on panels, protective cream on panels, and boxes were exposed to the thermal radiation of Shots 6 and 8 of Operation Snapper as part of Exercise Desert Rock IV. Exposures were made at 4, 5, 10 and 13 langleys (1 langley = 1 calorie per sq. cm.) Protection was measured with temperature indicators.

The clothing included standard items making up various ensembles, such as hot wet, hot dry, temperate, cold wet and cold dry. The fabrics on panels included essentially the same fabric combinations and various other fabrics to study reflectance, insulation, a variety of materials, including heat treated orlon, wool and synthetic fiber blends, and arrangements, including spacing and order of layers.

Except for a few items there was little damage at 5 langleys. The exceptions were the cotton nylon parka which shredded, the fur ruff which melted and the wool fabrics which scorched slightly. At 10 to 13 langleys all single layers of fabrics and all outer layers of fabric combinations were badly damaged. The damage to fabrics as clothing and on panels was about the same and any differences can be accounted for on the basis of angle of incidence.

Generally the damage was less for fabrics in contact with a solid backing. High reflectance reduced the damage. Wool was more sensitive than cotton at low intensities but less sensitive at high intensities. Blends of synthetics with wool up to 15 percent were about as resistant as wool but a 30 percent blend of dacron was damaged considerably. The heat treated orlon was very resistant. An aluminized cotton was very good.

There is still some uncertainty in interpreting protection from temperature indications and the conclusions are subject to revision. It seems, however, that the lighter ensembles, such as hot wet and hot dry, did not provide adequate protection in single layers for intensities of 10 to 13 langleys. Under pockets, seams, plaits and folds, the protection was adequate at this intensity. The temperate and heavier ensembles provided adequate protection at this level. Temperatures behind fabrics on panels were higher than behind clothing, largely on account of effects of angle of incidence and drape and spacing. White fabrics did not provide as much protection as might be expected from the resistance they offer to damage and generally not as much as dyed fabrics. Likewise the black heat treated orlon did not provide outstanding protection. The aluminized cotton was outstanding and for a corresponding weight provided more protection than any other fabric. Behind the black orlon most of this advantage was lost. The temperatures back of the camouflage shades were just slightly higher than for higher reflecting shades. There was no difference between the undyed and dyed frieze back of 9 oz. sateen, OG-107. Reversing the order of layers gave

[REDACTED]
UNCLASSIFIED

slightly lower temperatures as might be expected from the high reflectance of underwear fabric. Moving the 1/4 in. space from between backing and underwear to between underwear and undershirt had little effect. Varying the spacing had appreciable effect and 1/2 inch is much better than 1/16 in. The protection improves rapidly with increase in weight. All of these results are in fair agreement with results of previous tests or with principles established from them and from theoretical considerations.

QM protective cream afforded considerable protection and seemed to be adequate up to 13 langleys if used in layers 1/16 in. thick and possibly adequate if somewhat thinner.

The packaging test was not very successful. Very likely the inconsistent results were due to dust obscuration at the higher intensities. The temperatures of 56 to 74° C may be correct for 10 langleys but until corroborated they can be taken only as a lower limit.

- x -

[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]
UNCLASSIFIED

[REDACTED]
UNCLASSIFIED

CHAPTER 1

OBJECTIVES AND GENERAL PLAN

1.1 OBJECTIVES

Materials were exposed to the thermal radiation of two shots of Operation Snapper, in connection with Exercise Desert Rock IV. There were four phases of this test; studies of: 1. Clothing; 2. Clothing fabrics; 3. Protective cream; and 4. Packaging; with corresponding objectives;

(1) To determine the damage to and the protection afforded by standard clothing ensembles.

(2) To compare clothing fabrics exposed on flat panels, as to protection and damage, and to determine the importance of

- a. Reflectance, especially of camouflage shades.
- b. Spacing.
- c. Weight and number of layers.
- d. Arrangement of layers.
- e. Blending of wool and synthetic fibers.

(3) To determine the protection afforded by QM cream, protective flash burn.

(4) To determine the temperatures reached inside wood boxes.

1.2 HISTORY AND GENERAL PLAN

Fabric samples have been exposed in previous tests but clothing ensembles have not been studied. There have been no QM tests of protective cream or packaging. On the latter three items then the tests were of a preliminary nature, designed to learn how to test the items as well as to get specific data. The results of Operation Buster¹ showed that spacing affects the protection afforded by fabrics and accordingly the drape of clothing is important. Also, since the protection increases rapidly as the number of layers is increased, as shown at Operation Ranger² the effects of folds, pockets, seams and similar factors is important. It is difficult to simulate these effects on panels and so it seemed desirable to expose clothing on dummies. Since it was not possible to obtain full body dummies, torso dummies were used, exposing only upper body clothing. This was not entirely satisfactory but as Operation Upshot was at that time scheduled for the fall

- 1 - UNCLASSIFIED

[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]

of 1952 and additional clothing exposures were planned for that test and for Knothole, it seemed that torso dummies would give the information needed to plan for future tests.

Some other principles of protection were established in previous tests and it was desired to verify some of them and extend others. For example, white fabrics were resistant to damage but did not afford correspondingly better protection and since this did not seem to be generally accepted, one white fabric was included here. Camouflage shades absorbed a little more energy than standard military shades with corresponding poorer protection but the differences were small. Since the previous tests, two such shades were standardized and both were included, OG-107 on cotton and OG-108 on wool. Simulated skin temperatures were generally lower when the fabric was spaced from the backing and a few tests were included to determine whether the spacing distance is important. In spite of the extreme sensitivity of nylon, blends of nylon and wool were about as good as wool and accordingly, blends of wool and other synthetics were exposed in this test. All of the fabrics were exposed on flat panels.

The cold-bar suit utilizing the vapor barrier protection principle is undergoing extensive tests and a flat sample of the material was included here.

Standard QM items afford considerable protection but with the possibility of surprise and lack of time for evasive action, there is considerable concern about extensive burns on unprotected skin. Skin creams might protect parts of the body not usually covered, such as hands, face and neck and samples were included to determine the protection afforded by QM flash burn cream.

Future tests will include studies of damage to stores; in particular a packaging study is planned for Operation Knothole. To obtain data to permit better planning for that test, a preliminary study was made here which included determination of temperatures inside wood boxes at fairly high thermal intensities.

In all cases the basis of temperature measurement and protective value of various items was the performance of temperature indicators of the type used in both Ranger and Buster. Those used in this test were similar to those used at Buster with some improvement in a few individual cases and they were used in about the same manner as at Buster.

UNCLASSIFIED

CHAPTER 2

OPERATION AND GENERAL PROCEDURE

2.1 GENERAL

Samples were exposed at Shot 6 and Shot 8 of Operation Snapper on 25 May and 5 June 1952. Both of these were tower shots, about 300 feet high and both were predawn, about 0400 hours. The test areas are shown on the map on page 6 of the Test Director's Report³. Clothing on dummies and fabrics and protective cream on flat panels were exposed to energies of 4 to 13 langleys (1 langley = 1 calorie per sq. cm.). This was intended to be 6 to 15 langleys but the yields were lower than expected. Boxes were exposed on Shot 8 only at levels up to 42 langleys. Temperature indicators, unprotected and covered with thin transparent film were exposed at about 0.7 langleys.

2.2 THERMAL INTENSITIES

The actual exposures are listed in Table 2.1. No measurements of thermal radiation were made at these locations. The intensities were calculated from thermal yields supplied by the Armed Forces Special Weapons Project⁴, based on measurements made by the Naval Research Laboratory at the Control Point and measured atmospheric transmissibilities of 95 percent for Shot 6 and 94 percent for Shot 8. The distances for clothing, panels and unprotected indicators were approximately 1, 1-1/2 and 4 miles and when these approximate figures are used they will refer to the distances listed in Table 2.1.

The intensities for tower shots are always uncertain because of the possible attenuation of radiation by dust. Dust may be raised by the shock wave, travelling thru air or thru air and ground, or by the popcorn like bursting of soil particles exposed to intense thermal radiation of more than about 5 langleys⁵. For Shot 6 the samples at 1 and 1-1/2 miles were on high ground above ground zero, roughly on the opposite side of the tower from the troop location. The sample at 4 miles was near the troop location. It is not likely that dust affected these exposures. For Shot 8 all the samples were on fairly level ground. There were no internal inconsistencies in the results, however, for the samples of Shot 6 and those of Shot 8 at 1, 1-1/2 and 4 miles. There were inconsistencies for the closer samples of Shot 8 which possibly can be explained as due to dust obscuration.

2.3 WEATHER

Temperature and humidity data were also supplied by the Armed Forces

[REDACTED]

UNCLASSIFIED

Special Weapons Project⁴ and are given in Table 2.2. The values given are for measurements at the Control Point with the exception that the value at shot time was calculated for ground zero from the Control Point data.

2.4 REFLECTANCE AND TRANSMITTANCE OF MATERIALS

The reflectances of many of the fabrics of the ensembles, the fabrics for the panel exposures and the protective cream were measured with a General Electric Spectrophotometer. The nature of the variation with wave length is shown in Figs. 2.1 and 2.2; the curves for clothing items not shown are similar. The average reflectances for the outer layers of the clothing ensembles are given in Table 3.2 and for the panel fabrics in Table 4.2. The averages are for the ranges 0.4 to 0.7 μ and 0.7 to 1.0 μ , designated here as visible and infra red.

For some fabrics, such as the 9 oz. sateen dyed OD-7 or OG-107, the transmittance in the visible region is small, as measured for Operation Buster¹, generally less than 1/2 percent. For other fabrics, such as undyed or light colored or loosely woven fabrics it may be much higher. Measurements were made on a number of the fabrics using the General Electric Spectrophotometer in about the same manner as for Operation Buster. Much of the radiation is scattered and the result depends on the solid angle seen by the collector. The geometry was the same for all fabrics but there is some uncertainty about the exact value of the solid angle. The results are given in Fig. 2.3 and the average values in Tables 3.1 and 4.1.

2.5 TEMPERATURE INDICATORS

The indicators were of the same type used in Operation Buster. They were cut into pieces 1/4 in. by 1 in. and mounted in groups of 12, held face down in contact with the backing by adhesive tape along the ends. On the flat panels a fine line of latex cement along the center line was used in an attempt to improve the contact.

The indicators in the two groups were: M-5 paint, 48, 56, 62, 68, 74, 79, 84, 92, 100, 106, 118°C; 125, 133, 146, 157, 161, 175, 180, 205, 223, 240 and 257°C.

As yet there is not enough information to permit definite interpretation of temperatures in terms of skin injury. Results at Operation Ranger showed that the period of time during which the backing was at high temperature was very short and likely the maximum permissible temperature is considerably above the accepted value of 70°C for 1 second. A few preliminary results at the University of Rochester show that for

[REDACTED] UNCLASSIFIED [REDACTED]

UNCLASSIFIED

140°C
7
6

a 1/2 second exposure behind 2 layers of fabric, an indication of 14°C, on indicators arranged with essentially air backing, is about equivalent to a 2+ burn. This result needs verification but the value can be used tentatively until more complete results are available.

As before, the indicators show a range of temperatures rather than a single definite value. Each result is given as two values; the lower is the highest temperature for complete change and the temperature was certainly that high; the higher is the highest temperature for any change in the indicator and the temperature was probably nearly that high.

TABLE 2.1

Calculated Radiant Exposures

Distance from Ground Zero, ft.	Radiant Exposure langleys	Samples Exposed				Unprotected Indicators
		Clothing on Dummies	Fabrics on Panels	Protective Cream	Boxes	
				<u>Shot 6</u>		
5400	10.3	X	X	X		X
8400	4.2	X	X	X		X
21000	0.6					X
				<u>Shot 8</u>		
2910	41.6				X	
4110	19.3				X	
5210	12.7	X	X	X		X
5810	10.2				X	
8250	4.9	X	X	X		X
20000	0.7					X

TABLE 2.2

Temperature and Relative Humidity. All data at the Control Point except for H Hour; H hour result calculated for shot area

Approx. Time Hours	Shot 6		Shot 8	
	Temperature	Relative Humidity	Temperature	Relative Humidity
H-3-1/2	61°F	35%	67°F	34%
H-2-1/2	58	38	65	36
H-1-1/2	59	42	63	39
H- 1/2	57	42	62	39
H	57	41	64	45
H+ 1/2	57	46	60	44

UNCLASSIFIED

SHOTS AREA
Y
NOT

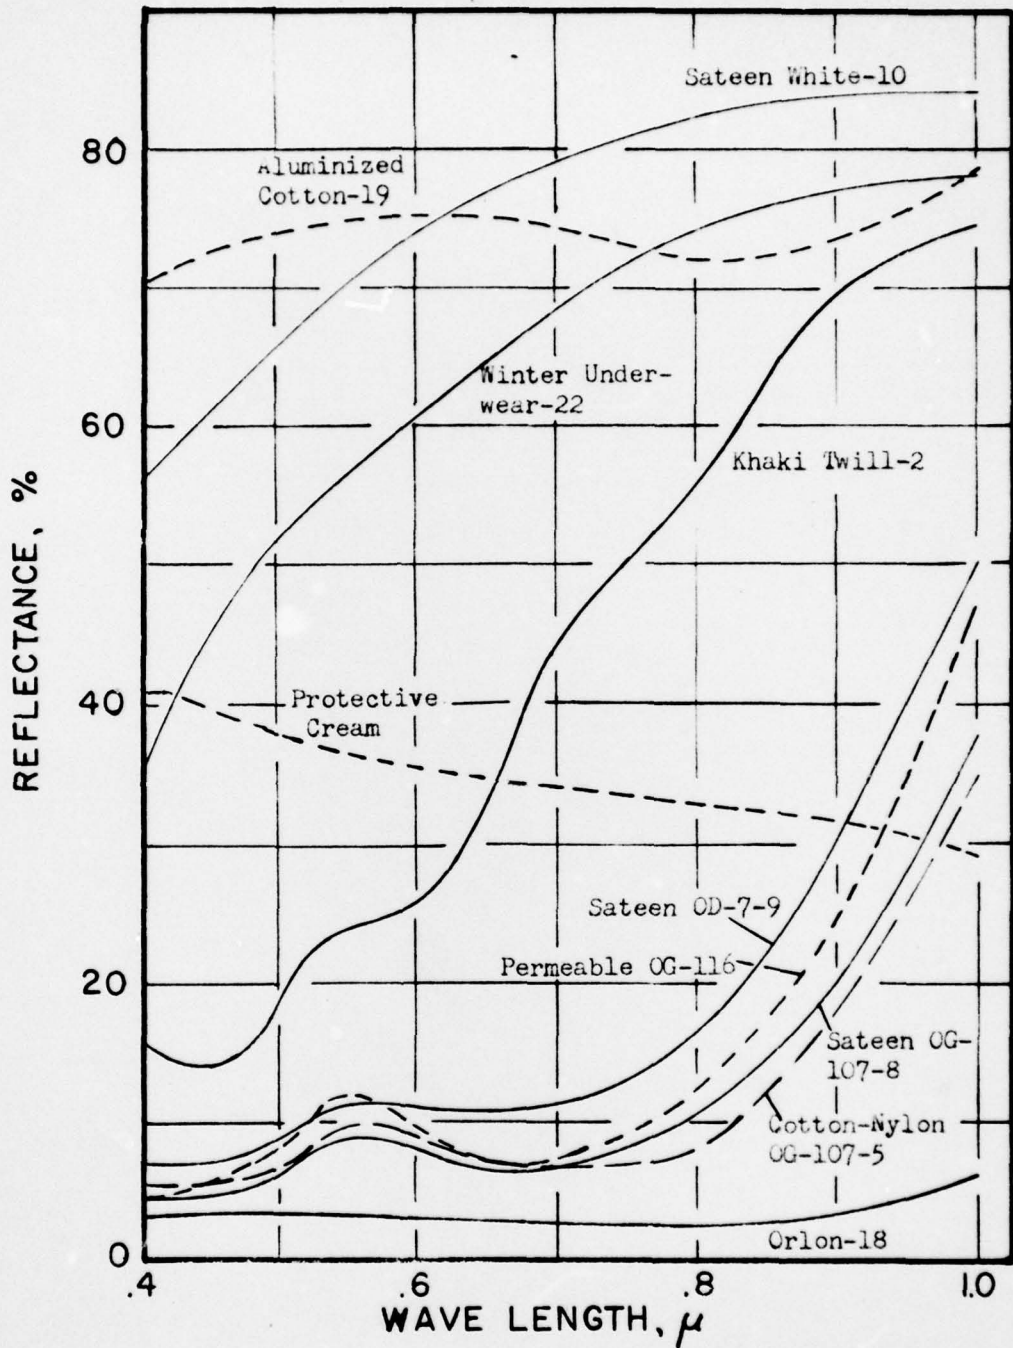


Fig. 2.1 Reflectance of Cotton and Orlon Fabrics and Protective Cream. Numbers refer to Table 4.1

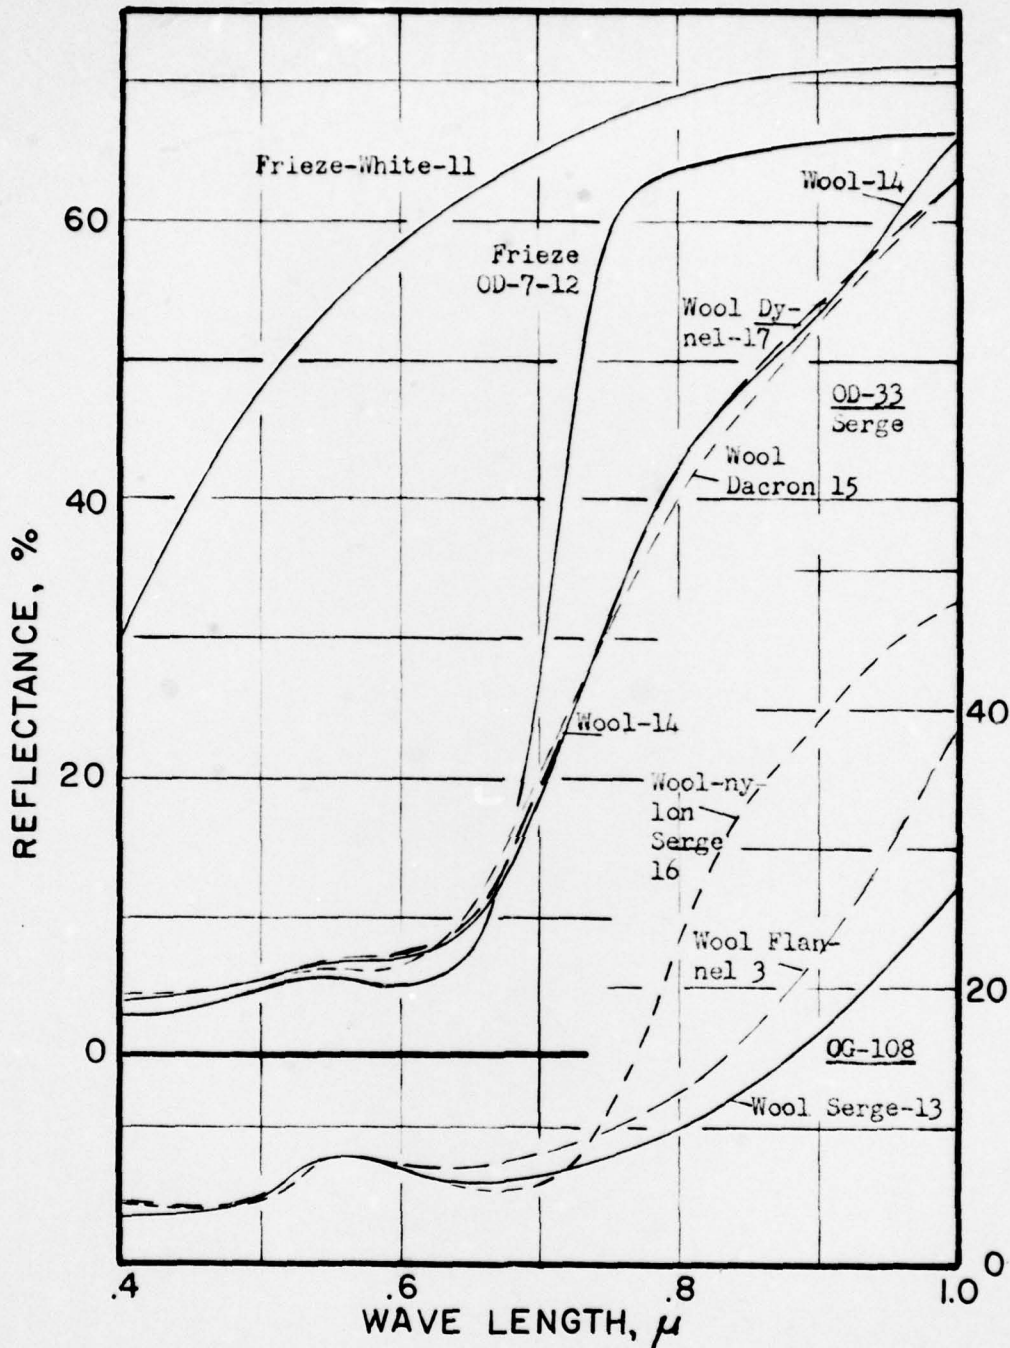


Fig. 2.2 Reflectance of Wool Fabrics.
Numbers refer to Table 4.1

UNCLASSIFIED

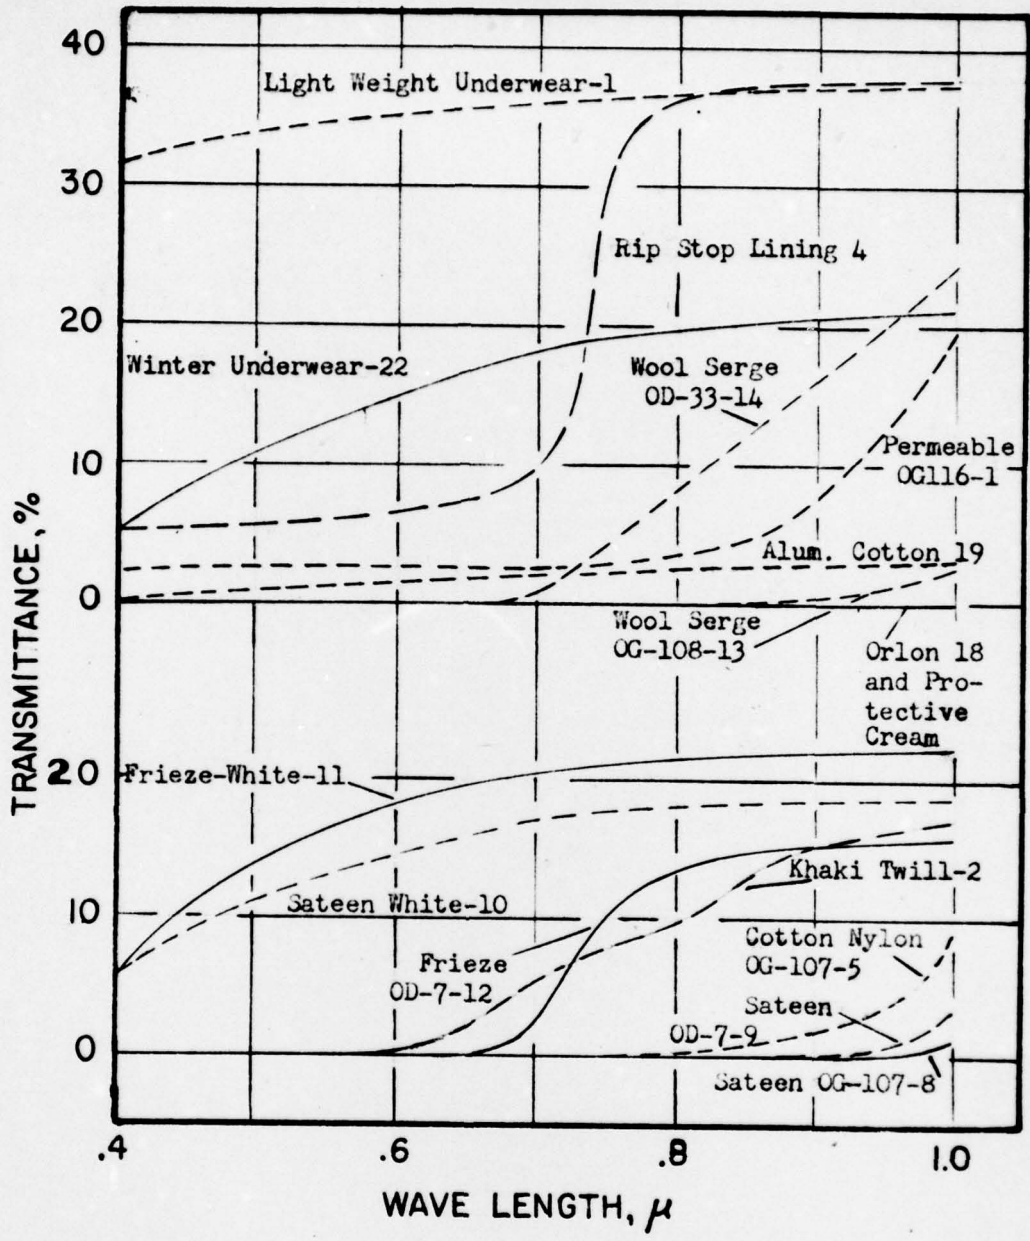


Fig. 2.3 Transmittance of Materials. Numbers refer to Table 4.1

[REDACTED]
UNCLASSIFIED

CHAPTER 3

CLOTHING ON DUMMIES

3.1 PROCEDURE AND MATERIALS

The plan was to expose 5 ensembles; hot dry, hot wet, temperate, cold wet and cold dry. At the time of the test, however, the hot dry and hot wet ensembles were not yet standardized. Accordingly substitutes were used; the 8.2 oz. uniform twill shirt khaki I and light-weight under shirt, white, for the hot dry ensemble and the 5.5 oz. permeable cotton OG-116 or 6 oz. wind resistant sateen shirt OD-7 and the light weight undershirt, white, for the hot wet ensemble. In referring to these ensembles they will be designated hot wet and hot dry. The temperate combination included part of the cold wet ensemble; for Shot 6, undershirt, shirt and jacket without liner and for Shot 8, undershirt and shirt. The clothing exposed on each shot is listed in Table 3.1. The average reflectance of the outer layers and the average transmittance of some layers are given in Table 3.2. The ensembles were exposed on dummies shown in Fig. 3.1. To measure the protection, the temperature indicators described in Section 2.5 were placed as shown. In addition for the cold dry ensemble the dummies were fitted with heads to accommodate the hoods and sets of indicators were placed on each cheek to indicate high temperatures that might be reached if the ruff burned.

3.2 DAMAGE TO CLOTHING

In general there was little damage to clothing exposed to 4 to 5 langleys at about 1-1/2 miles, but severe damage to outer layers exposed to 10 to 13 langleys at about 1 mile. In some cases there was considerable damage to underlying layers, such as underwear under the lightweight outer garments and lining of jackets. The clothing varied in weight and number of layers, type of material and shade and the angle of incidence varied over the surface of each garment. Consideration of these variables accounts for much of the difference in damage.

As is usually the case in field tests of this kind, it is difficult to assess separately the damage from thermal and from blast effects. In some cases possibly the radiation weakened the fabric and the wind blew it away. At any rate parts of garments were gone and it is not possible to say whether they afforded some protection during the flash or were burned away very quickly.

Photographs taken at the site are shown in Figs. 3.2 to 3.21. Since there was little visible damage at less than 6 langleys except

- 9 - UNCLASSIFIED
[REDACTED]
[REDACTED] 1946

[REDACTED]

UNCLASSIFIED

for small effects of the blast the photographs of samples at 1-1/2 miles generally will serve to indicate the condition of all the clothing before exposure. The scorching of the dummies and under layers is shown in Figures 3.22 and 3.23.

3.2.1 Hot Wet Ensemble

Shot 6

4 Langleys at 1-1/2 Miles

No visible damage to jacket or undershirt.

10 Langleys at 1 Mile

Jacket. Badly burned. Single layer areas burned away, also outer layer of shoulder, collar and pockets and center plait. Some remaining fragments charred black. Underlying layers of jacket scorched.

Undershirt. Under a single layer of jacket undershirt was scorched badly, dark brown. Some scorching around edges of collar and pockets but little scorching at center of pocket area. Undershirt shows effect of drape; it fitted snugly on the dummy and the jacket hung away from the undershirt near the waist with less scorching of the underwear. This is shown in the photograph of Figure 3.23.

Shot 8

5 Langleys at 1-1/2 Miles

No visible damage to jacket or undershirt.

13 Langleys at 1 Mile

Jacket. Similar to corresponding position, Shot 6, but burned more. Practically all single layer fabric gone and most of outer layer of multilayer sections. Buttons scorched.

Undershirt. Scorched and burned under single layers of jacket. Badly scorched on shoulders. Shows effect of drape as for Shot 6.

3.2.2 Hot Dry

Shot 6

4 Langleys at 1-1/2 Miles

No damage to shirt or undershirt.

16 Langleys at 1 mile

Slight scorching on front of shirt; fabric intact. No damage to undershirt.

[REDACTED]
[REDACTED]
1946

[REDACTED]

UNCLASSIFIED

[REDACTED]

UNCLASSIFIED

3.2.4

Cold Wet

Shot 6

4 langleys at 1-1/2 miles

No visible damage to any garment.

10 langleys at 1 mile

Similar to temperate but slightly less damage. Some of front charred and burned away. Left side worse than right. Under layers scorched where top layer was burned away or charred badly and still in place.

Under Layers. Pile liner scorched slightly, mainly on left side.

Shot 8

5 langleys at 1-1/2 miles

No visible damage to any garment.

13 langleys at 1 mile

Jacket. Damaged more than similar ensemble in Shot 6 or Temperate in Shot 6. Enough of top layer burned to expose under layers. Steen lining and undyed buckram and drill interliners were scorched. Under side of left pocket was scorched considerably indicating outer layers were burned away before flash was over.

Under Layers. The pile liner was scorched over most of the front but especially in the upper chest area. The collar of the wool shirt was scorched where exposed but not damaged otherwise. No scorching of undershirt.

3.2.5

Cold Dry

Shot 6

4 langleys at 1-1/2 miles

No visible damage to any garment except fur ruff on hood. Outer ends of wolverine fur burned or melted to a depth of about 3/4 inch. Synthetic ruff not damaged.

10 langleys at 1 mile

Parka. Most of front surface gone. In places the nylon filling yarn melted leaving the cotton warp unsupported. Over most of the area all the fabric was gone. The natural fur ruff was burned and melted, worse than for exposure at 6 cal. per sq. cm. The nylon ruff was damaged more, almost all melted.

Under Layers. The pile liner for the parka was badly

[REDACTED]

UNCLASSIFIED

[REDACTED]

UNCLASSIFIED

scorched especially in the upper chest area. Other layers not affected.

Shot 8

5 langleys at 1-1/2 miles

Parka. Over much of the front area the nylon filling was melted leaving the fabric shredded. Generally there were small areas and the garment as a whole remained in place.

Under Layers. There was no visible damage on the pile liner or other layers.

13 langleys at 1 mile

Parka. The front surface was burned or blown away with evidence at the edges of the melting of the nylon filling.

Under Layers. The pile liner of the parka was badly scorched, dark brown in places. There was no visible damage to other garments.

3.2.6 Summary

In general the results are about as expected from previous tests. The intensities of radiation were lower than expected and probably more information would have been obtained by exposing the heavier clothing at higher intensities. With the exception of the shredding of the nylon filled parka, the melting of the fur ruff and the scorching of the wool shirt, there was no visible damage up to 5 langleys. At 10 to 13 langleys the lighter clothing and the outer layers of the heavier clothing were very badly damaged and would afford little or no protection after the flash.

In all cases the khaki shirt was damaged less than the OD-7 or OG-107 garments. In some cases it was a little heavier but likely most of the difference was due to its higher reflectance.

The effect of angle of incidence is evident in the non-uniform scorching and charring^{of} both for fairly smooth curved surfaces and for fairly flat surfaces which were not smooth.

The effect of spacing between layers is evident in the effect of drape in keeping the outer layers from making contact with the underwear.

The effect of added layers is evident from the protection afforded by seams, folds, plaits, collars and pockets. For an erect

[REDACTED]

UNCLASSIFIED

soldier, the upper chest, above the pockets, seems to be a place of maximum damage, partly because the beam is incident at nearly zero angle and also there are fewer layers in that area.

The natural fur ruff was damaged slightly at 4 langleys but withstood 10 langleys better than the nylon ruff which was completely melted. Neither seems to be satisfactory in this respect.

The nylon filled cotton outer layer of the parka performed very poorly. This might be expected from previous tests on all nylon fabrics. Likewise, previous experience indicates that blends of synthetics with wool perform nearly as well as wool alone and possibly blends of nylon with cotton will also show resistance to damage. If the desired properties cannot be achieved at low weight in this way then some more resistant material should be substituted for the nylon.

The wool shirt was badly damaged but the slight scorching of the undershirt indicates that ~~it~~ ^{the shirt} remained in place and afforded considerable protection.

Although as indicated by the lack of scorching of underlayers and the temperature indicator results given later, the heavier clothing provided adequate protection, it should be realized that in some cases the outer garment was damaged so badly that it would not afford adequate protection after the flash. For example, the parka exposed to 10 to 13 langleys would not protect a soldier against wind or rain and even if he survived the atomic blast probably he could not survive against the elements afterward.

3.3 PROTECTIVE VALUE OF CLOTHING

It is obvious from the effects of angle of incidence, drape and variation in thickness and number of layers that a large number of indicators would be needed to determine the maximum temperature attained and the range to be expected. Of the seven sets of indicators used, one was essentially a control, two were under the arms where the angle of incidence was high, one was on the chest where the angle of incidence was low but generally more than the minimum number of layers was over the indicator, one was at the waist and again under a number of layers, two were on the shoulders where there were usually added layers and also where the angle of incidence was high. The scorching of under garments, for example the undershirt for the hot wet ensemble at 10 langleys in Shot 6 and 13 langleys in Shot 8, and the pile jacket liner for the cold wet ensemble at 13 langleys in Shot 8, shown in Fig. 3.23, show that the most vulnerable spot is the upper chest, above the pockets. No indicators were placed there. Although the temperature indicators may show adequate protection for the locations measured, this does not insure

[REDACTED]

[REDACTED]

UNCLASSIFIED

[REDACTED]
UNCLASSIFIED

that temperatures sufficient to cause injury were not reached in a few spots.

3.3.1 Hot Wet

Generally, the temperatures were from 48 to 106°C. At 5 langleys the highest temperature recorded was 62°C; at 13 langleys 106°C.

3.3.2 Hot Dry

The temperatures were slightly lower than for the Hot Wet ensemble, a maximum of 62°C at 5 langleys and 74°C for 13 langleys.

3.3.3 Temperature

The temperatures both with the jacket and the wool shirt were about the same as for the Hot Dry ensemble.

3.3.4 Cold Wet

The highest temperature recorded was 48°C and ~~only~~ that high in ^{ONLY} a few cases.

3.3.5 Cold Dry

The temperature was below that of the most sensitive indicator in all cases. Temperature indicators on the side of the face of the dummies equipped with hoods showed no consistent indication of high temperatures from the burning or melting ruff. At 4 langleys both sides may have reached as high as 48°C. At 10 langleys there were spot-ty indications of 56°C on the right side (nylon) and 118°C on the left side (fur). The temperatures here will depend very greatly on the contact with or proximity of ruff to skin as well as damage to the ruff.

3.3.6 Summary

The highest temperatures recorded were probably below the limit for second degree burns if the 141°C figure is accepted. However, the scorching of the dummies and underwear indicates that the maximum temperatures were above the maximum recorded. The hot dry and hot wet ensembles do not provide adequate protection at 10 to 13 langleys where there is only a single layer of the outer fabric but they do in multilayer

UNCLASSIFIED

[REDACTED]

areas, such as the pocket, collar and waist locations. The temperate, cold wet and cold dry ensembles afford adequate protection at 13 lang-
leys.

With some modification to improve the protection in the upper chest area the above uncertainty would be eliminated for the front of the upper body. However, other areas are about equivalent to the upper chest. Exposures were not made on sleeves, backs or legs but they are equally vulnerable and would not offer adequate protection for radiation of this intensity at normal incidence.

Even though the heavier ensembles provide adequate protection at this level and probably at higher levels, it should be emphasized again that although the soldier would likely survive the atomic blast the outer clothing would be so severely damaged that it would not provide adequate environmental protection.

There are differences between the ensembles which would likely be greater at higher intensities. The hot dry ensemble was better than the hot wet. It is slightly heavier but likely most of the difference is due to its higher reflectance. The relatively light hot dry was nearly as good as the heavier temperate, again probably because of the higher reflectance. The very good protection of the cold wet and cold dry ensembles is mainly a matter of thickness and weight.

RESERVED
[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]

UNCLASSIFIED

UNCLASSIFIED

TABLE 3.1

Clothing Ensembles

Fabric layers are in order, first layer exposed, last layer next to dummy

Type	Garment		Fabric		Nominal Weight oz/yd ²	Shade
	Name	Spec.	Name	Spec.		
Hot Wet	Shot 6 Jacket, Light Weight	Experimental Model JAN-U-797	Cl. Ctn. Permeable	MIL-C-10859A	5.2	00-116
	Under Shirt, Ctn. Quarter Sleeve		Cl. Ctn. Knitted		$\frac{3.0}{8}$	White
Hot Dry	Shot 8 Jacket, Light Weight	MIL-J-3175	Cl. Ctn. Wind Re- sistant, Poplin	MIL-C-342A	6.5	00-7
	Under Shirt, Ctn. Quarter Sleeve	JAN-U-797	Cl. Ctn. Knitted		$\frac{3}{9}$	White
	Shirt, Ctn. Stand-Up Collar, Khaki	MIL-S-3011- B-A-1	Cl. Ctn. Uniform Twill	JAN-C-298	8.2	Khaki I
Temperate	Under Shirt, Ctn. Quarter Sleeve	JAN-U-797	Cl. Ctn. Knitted		$\frac{3.0}{11}$	White
	Shot 6 Jacket Shell, M-1951	MIL-J-11445 (QMC)	Cl. Ctn. Wind Re- sistant, Sateen	MIL-C-557A	9	00-107
	Shirt, Field, Wool	MIL-S-10858 (QMC)	Cl. Ctn. Wind Re- sistant, Oxford	MIL-C-484	5.5	00-107
Shot 5	Undershirt, Winter, M-50	MIL-U-10211B	Cl. Wool	MIL-C-10752	10.3	00-108
	Shirt, Field, Wool		Cl. Wool & Cotton (50/50/Knitted)		$\frac{10.5}{35}$	Grey
Shot 5	Shirt, Field, Wool	MIL-S-10858 (QMC)	Cl. Wool	MIL-C-10752	10.3	00-108
	Shirt, Field, Wool					

UNCLASSIFIED

TABLE 3.1 (cont'd)

Clothing Ensembles
 Fabric layers are in order, first layer exposed, last layer next to dummy

Type	Garment		Spec.	Name	Fabric	Nominal Weight oz/yd ²	Shade
	Name	Spec.					
Cold Wet	Jacket, Shell, Field, M-50	Undershirt, Winter, M-50	MIL-U-10211B	Cl. Wool & Cotton (50/50/Knitted)	MIL-C-557	9	Grey
		Jacket, Shell, Field	MIL-J-11448 (QMC)	Cl. Ctn. Wind Be- sistant, Sateen	MIL-C-484	5.5	OG-107
	Liner, Jacket, Field		MIL-L-11449 (QMC)	Cl. Ctn. Wind Be- sistant, Oxford	MIL-C-10772A	1.8	OD-7
		Shirt, Field, Wool		MIL-S-10858 (QMC)	Cl. Rayon, Acetate (Saponified) Rip Stop	MIL-C-10751 17	17
Cold Dry	Parka Shell, M-1951	Under Shirt, Winter, M-50	MIL-U-10211B	Cl. Wool	MIL-C-10752 10.3	10.3	Grey
		Parka Shell, M-1951	MIL-P-11013 (QMC)	Cl. Wool & Cotton (50/50) Knitted	MIL-C-10829 5.0	5.0	OG-107
	Parka Liner, M-51		MIL-P-11012 (QMC)	Cl. Ctn. Warp, Nylon Filled, Oxford	MIL-C-10772A	1.8	OD-7
		Jacket, Shell, Field, M-1951		MIL-J-11448 (QMC)	Cl. Rayon, Acetate (Saponified) Rip-Stop	MIL-C-10751 17	17
				Cl. Mohair, Frieze Double Face	MIL-C-557A 9	9	OG-107
				Cl. Ctn. Wind Be- sistant, Sateen	MIL-C-484 5.5	5.5	OG-107

UNCLASSIFIED

RESTRICTED DATA
 ATOMIC ENERGY
 JAN 1950

UNCLASSIFIED

UNCLASSIFIED

TABLE 3.1 (cont'd)

Clothing Ensembles

Fabric layers are in order, first layer exposed, last layer next to dummy

Type	Garment	Name	Spec.	Name	Spec.	Nominal Weight oz/yd ²	Shade
	Liner, Jacket Field, M-1951		MIL-L-11149 (QMC)	Cl. Rayon, Acetate (Saponified) Rip-Stop	MIL-C-10772A	1.8	OD-7
	Shirt, Field, Wool		MIL-S-10556 (QMC)	Cl. Mohair, Friese, Double Face Cloth, Wool	MIL-C-10751	6.4	White
	Under Shirt, Winter, M-50		MIL-U-10211B	Cl. Wool and Cotton (50/50) Knitted	MIL-C-10752	10.3	OG-107
	Hood, Parka, M-1951		MIL-H-11023	Cl. Ctn. Warp, Nylon Filled, Oxford	MIL-C-10829	10.5	Grey
				Cl. Wool, Lining	MIL-C-2069		OG-107
				Fur Strips: one side Wolverine, one side Nylon	MIL-F-11861		OD-33

UNCLASSIFIED

TABLE 3.2

Reflectance & Transmittance of Outer Layers of Clothing
Fabrics. Averages for Visible & Near Infra Red Regions

<u>Item</u>	<u>Ensemble</u>	<u>Shade</u>	<u>Reflectance, %</u>		<u>Approx. transmittance, %</u>	
			<u>V</u>	<u>IR</u>	<u>V</u>	<u>IR</u>
Jacket, Light Wt.	Hot Wet	OG-116	8. a	21.5 ^a	2.5 ^b	2.5 ^b
" " "	" "	OD-7	7.5 ^a	18. a		
Shirt, Uniform Twill	Hot Dry	Khaki I	25. b	62. b	1. b	12. b
Shirt, Wool, Flannel	Temperate	OG-108	6. b	19. b		
Jacket, Field	Temperate and Cold Wet	OG-107	6. a	15.5 ^a	< 0.5 ^b	< 0.5 ^b
Parka	Cold Dry	OG-107	7.5 ^a	17.5 ^a	< 0.5 ^b	2. b

Note: If measured on garment, data are marked a; if on corresponding fabric, marked b.

[REDACTED]

UNCLASSIFIED

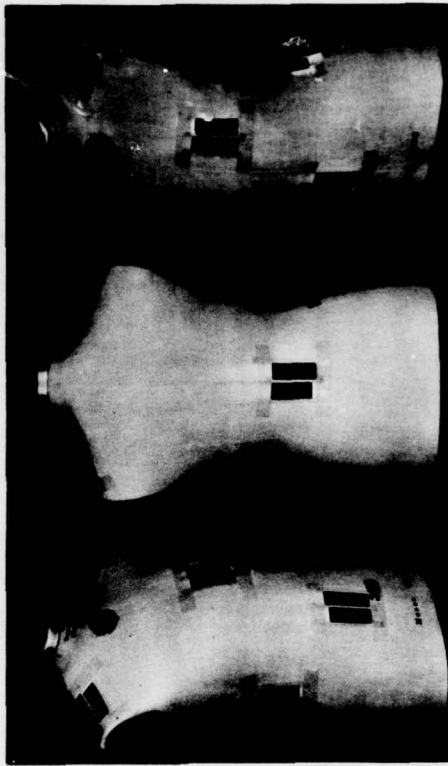


Fig. 3.1 Dummies with Temperature Indicators

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.2 Shot 6 - 1-1/2 Miles Hot Wet

[REDACTED]

UNCLASSIFIED

[REDACTED]
[REDACTED]GY
[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.3 Shot 6 - 1-1/2 Miles Hot Dry

24

--25--

[REDACTED]

UNCLASSIFIED

[REDACTED]
[REDACTED] 1916

[REDACTED]
UNCLASSIFIED



Fig. 3.4 Shot 6 - 1-1/2 Miles Cold Wet

25
- 26 -

UNCLASSIFIED
[REDACTED]
[REDACTED] 01
[REDACTED] 26

[REDACTED]

UNCLASSIFIED



Fig. 3.5a Shot 6 - 1-1/2 Miles Cold Dry.
Before Exposure.

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.5 Shot 6 - 1-1/2 Miles Cold Dry

[REDACTED]

UNCLASSIFIED
[REDACTED]
[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.6 Shot 6 - 1 Mile Hot Wet

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]
UNCLASSIFIED



Fig. 3.7 Shot 6 - 1 Mile Hot Dry

[REDACTED]

UNCLASSIFIED
[REDACTED]
[REDACTED]
6

[REDACTED]

UNCLASSIFIED



Fig. 3.8 Shot 6 - 1 Mile Temperate

[REDACTED]

UNCLASSIFIED

[REDACTED] CA
ATOMIC ENERGY
[REDACTED]

[REDACTED] UNCLASSIFIED



Fig. 3.9 Shot 6 - 1 Mile Cold Wet

[REDACTED]

UNCLASSIFIED

[REDACTED]
ARMED ENERGY
APR 1946

[REDACTED]

UNCLASSIFIED



Fig. 3.10 Shot 6 - 1 Mile Cold Dry

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.11 Shot 8 - 1-1/2 Miles Hot Wet

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED] 1946

[REDACTED]

UNCLASSIFIED



Fig. 3.12 Shot 8 - 1-1/2 Miles Hot Dry

[REDACTED]

UNCLASSIFIED

[REDACTED]
[REDACTED]
[REDACTED] 1946

[REDACTED]

UNCLASSIFIED



Fig. 3.13 Shot 8 - Before Exposure
Temperate

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.14 Shot 8 - 1-1/2 Miles Temperate

[REDACTED]

UNCLASSIFIED

[REDACTED] DATA
[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.15 Shot 8 - 1-1/2 Miles Cold Wet

UNCLASSIFIED

[REDACTED]

[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.16 Shot 8 - 1-1/2 Miles Cold Dry

[REDACTED]

UNCLASSIFIED

[REDACTED] CA
[REDACTED] 10/18

[REDACTED]

UNCLASSIFIED



Fig. 3.17 Shot 8 - 1 Mile Hot ~~Day~~ WET

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.18 Shot 8 - 1 Mile Hot Dry

[REDACTED]

UNCLASSIFIED

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.19 - Shot 8 - 1 Mile Temperate

UNCLASSIFIED

[REDACTED]

[REDACTED]

[REDACTED]

UNCLASSIFIED



Fig. 3.20 - Shot 8 - 1 Mile Cold Wet

[REDACTED]

UNCLASSIFIED

[REDACTED]
[REDACTED] DATA
[REDACTED] Y

[REDACTED]

UNCLASSIFIED



Fig. 3.21 Shot 8 - 1 Mile Cold Dry

[REDACTED]

UNCLASSIFIED

[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]

UNCLASSIFIED

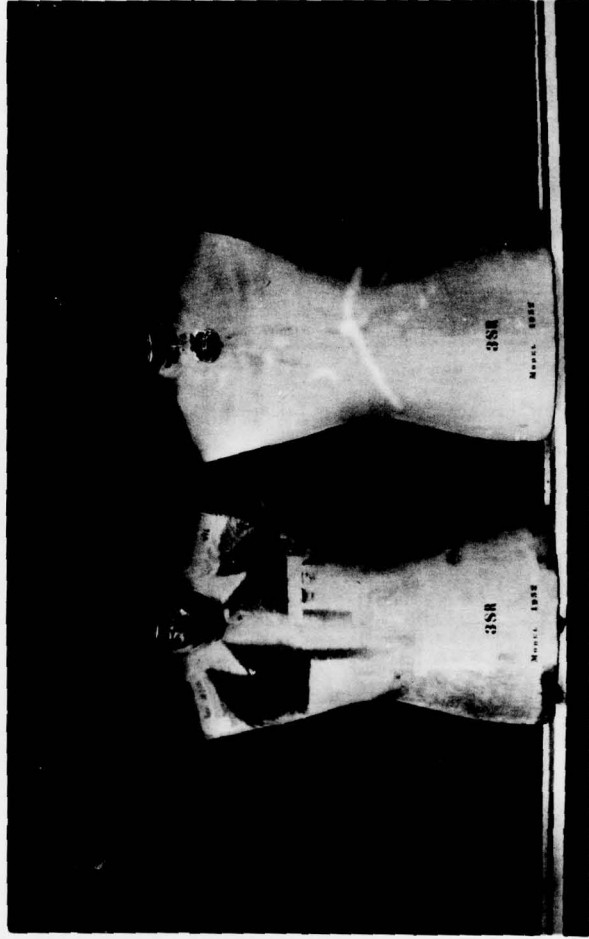


Fig. 3.22 Scorching of Dummies under Hot Wet and Hot Dry Ensembles, 1 Mile, Shots 6 & 8

[REDACTED]


UNCLASSIFIED

[REDACTED]
[REDACTED] RGY



Fig. 3.23 Scorching of Under Layers, 1 Mile, Hot Wet Shot
6, Hot Wet Shot 8, Cold Wet Shot 8





UNCLASSIFIED

CHAPTER 4

FABRICS ON PANELS

4.1 PROCEDURE

The same clothing ensemble fabrics were exposed on flat panels and in addition other fabrics and combinations were used to determine the effect of reflectance, transmission, and spacing; the effect of blending wool with synthetic fibers, and the protective value of the cold bar ensemble.

4.1.2 Method of Mounting

The panels were the same type used in Operation Buster². They were of white pine about 8 in. square with about half the sample in contact with the backing and the other half spaced 1/4 in. from the backing. The backing had a reflectance of about 56 percent in the visible and 93 percent in the near infrared. In this experiment the wood panel was backed with 1/4 in. plywood. The samples were mounted on an angle iron frame with about 2 in. spacing between samples. These are shown in Fig. 4.1. The frame was adjusted for normal incidence.

To measure the protective value, the passive indicators described in Section 2.5 were placed behind the fabrics.

4.2 FABRICS



For each shot there were 16 samples; these were not exactly the same for the two shots. They are listed in Table 4.1, which also gives some properties of the fabrics including weight and average reflectance and transmittance. The reflectance and transmittance are also shown in Figs. 2.1, 2.2 and 2.3. The repeated values in Table 1 represent a measurement on a single sample of the fabric.

4.3 DAMAGE TO FABRICS

4.3.1 Photographs

Photographs of the panels are shown in Figs. 4.1 to 4.4. With few exceptions there was little or no damage at 5 langley's and the materials before exposure were essentially the same as after exposure at 1-1/2 miles.

UNCLASSIFIED



[REDACTED]

UNCLASSIFIED

4.3.2 Damage Code

For convenience in recording a code of damage was used; it was about the same as that in Operation Ranger and is given below.

<u>Rating</u>	<u>Damage to each surface</u>
0	No perceptible damage
1	Barely perceptible damage cotton - very slightly scorched; wool and blends of wool with synthetics - singed.
3	Appreciable damage cotton - very definite scorches; wool and wool blends - singed and trace of melting.
5	Severe damage cotton - badly scorched and beginning of charring; wool and wool blends - melted.
7	Very severe damage cotton - charred, dark brown; wool and wool blends - melted, little or no trace of weave pattern.
9	Extreme damage cotton - charred very dark brown or black; wool and wool blends - thick layer on surface melted and dark in color.

<u>Rating</u>	<u>Overall Damage</u>
0	No perceptible damage, intact.
1	Slightly torn or burned, almost intact.
3	Considerable tearing or burning, up to half of sample gone.
5	More than half gone.
7	Nearly all gone.
9	All gone.

The rating then includes 3 digits, the first for the face, the second for the reverse side and the third overall; e.g., a rating of 000 indicates no perceptible damage at all; 955 indicates extreme damage

UNCLASSIFIED

[REDACTED] TA
ACF 1746

[REDACTED]

UNCLASSIFIED

on the face, severe damage on the reverse side and more than half the sample missing. Where the sample was missing or so little left that the thermal damage could not be estimated, that is indicated by - - 9.

4.3.3 Damage at Low Intensities Radiant Exposures.

There was very little damage at 4 to 5 langleys. The only visible effect was on the following:

Sample 5, some damage to the nylon of the cotton warp-nylon filled oxford, rating 111.

Samples 13, 14, 15, 16 and 17, serges of wool and blends of wool and synthetics, slight singeing, with ratings of 100.

Samples 18 and 19, Orlon, heat treated, slight shininess, rating 100.

4.3.4 Damage at 10 to 13 Langleys

The damage at 10 and 13 langleys is summarized in Table 4.2.

4.3.4.1 Fabrics Equivalent to Clothing Ensembles

The damage to fabrics on the panels was about the same as the maximum damage to the same fabrics as clothing. The nylon filled cotton warp oxford on sample 5 was slightly damaged at 5 langleys and completely destroyed at 13 langleys.

4.3.4.2 Reflectance

The undyed sateen, sample 10, was much more resistant than either OD-7 or OG-107 with no perceptible damage at 13 langleys. Dyed samples were almost completely destroyed at that intensity. The aluminized fabric showed no damage up to 10 langleys.

There were slight but apparently definite differences between standard and camouflage shades. For cotton, OG-107, e.g., sample 8, was damaged more than OD-7, sample 9. For wool, OG-108, sample 13, was damaged more than OD-33, sample 14.

4.3.4.3 Backing and Under Layers

The spaced samples; i.e., with air backing, were damaged

UNCLASSIFIED

UNCLASSIFIED

[REDACTED]

Fabrics with air backing were damaged more than those in contact. Under layers were scorched more for the contact condition than for the spaced arrangement. The damage to the surface fabric in multi-layer systems was about the same as for contact with a wood backing.

The damage to fabrics exposed as clothing varied considerably but the maximum damage was similar to that of fabrics on flat panels.

Whenever comparisons are possible the results here are in agreement with the results of previous tests or with principles evident from those tests.

4.4 PROTECTIVE VALUE OF FABRICS

The temperatures shown by the indicators behind the fabrics are given in Table 4.3. As is the usual experience with these indicators, generally the indication is not a single temperature but a range of temperatures. The first figure is the highest temperature for which the change was complete; the second figure is the highest for which there was any definite indication of change. Generally this range is sufficiently small to give useful results. For similar sample, for which a direct comparison is desirable, visual examination will sometimes show differences not necessarily obvious in the table; i.e., it is possible to determine a difference between fabrics even though that difference cannot be expressed qualitatively.

Generally, the temperatures were higher for the higher ^{ENERGIES} intensities and lower for the spaced sample than for contact. Comparisons between fabrics must be made under comparable conditions.

4.4.1 Fabrics Equivalent to Clothing Ensembles

The temperatures were highest for Sample 1, the hot wet combination of 5.2 oz. cotton permeable and light weight underwear, with temperatures up to 106°C at 5 langleys and up to 223°C at 13 langleys. They were considerably lower for sample 2, the hot dry combination of 8.2 oz. khaki uniform twill and light weight underwear, up to 180°C at 13 langleys. The twill is slightly heavier than the permeable but most of the difference is in reflectance, an average of about 40 percent for the khaki compared to about 15 percent for the permeable. For sample 3, the combination of 9 oz. sateen, 10.3 oz. wool flannel and 10.5 oz. winter undershirt, there was considerable variation in protection with intensity. At low intensities this combination was better than Sample 2 but at 15 cal. per sq. cm. it was not. The effects of weight and reflectance can be balanced but the balance seems to depend on intensity. For samples 4 and 5, corresponding approximately to the cold wet and cold dry

UNCLASSIFIED

[REDACTED]

[REDACTED]

ensembles, the maximum temperature was 56°C and generally the lowest indicators were just on the verge of changing.

4.4.2 Effect of Reflectance

Samples 8, 9 and 10 are of the same basic fabric, 9 oz. W.R. sateen; sample 10 undyed, sample 9 dyed with the old standard OD-7 and sample 8 dyed with the current standard OG-107. The average reflectances are about

	<u>Visible</u>	<u>Near Infrared</u>
Undyed	69.	83.
OD-7	9.5	26.
OG-107	6.5	18.

Up to 1.0 μ , the OD-7 and OG-107 samples transmit very little light; the value for the undyed fabric is roughly 15 percent.

Temperatures were generally slightly hotter for the OG-107 than for OD-7 as indicated below:

<u>EXPOSURE</u> <u>Intensity</u> <u>langleys</u>	<u>Contact</u>		<u>Spaced</u>	
	<u>OD-7</u>	<u>OG-107</u>	<u>OD-7</u>	<u>OG-107</u>
6	68-92	79-106	62	62
6	74-106	68-133	56-62	62
15	133-223	146-257	100-175	146-257
15	157-257	133-257	125-257	146-240

The differences are small but apparently definite and in accordance with the differences in reflectance and in agreement with the results of Operation BUSTER¹.

The undyed fabric was exposed only on Shot 8. For that case the temperatures were generally higher than for the corresponding dyed fabrics. At 5 langleys, in contact the protection was about the same as for OG-107 but spaced it was considerably less; at 13 langleys the temperatures were very high, for both contact and spaced. This lower protection afforded by undyed fabrics and especially the lack of difference between contact and spaced fabrics is also in agreement with results of Operation BUSTER¹.

4.4.3 Transmittance of Under Layers

If any appreciable part of the energy transferred to the backing by radiation, possibly from hot fabric, it might be expected that

the transmittance of underlying layers would be important. The difference between samples 11 and 12 is in the color of the frieze, undyed for sample 11 and OG-108 for sample 12. There is little difference in protection but apparently the undyed frieze was consistently slightly better. Possibly the difference in effective transmission is very small or the effects of differences in transmittance were overshadowed by differences in structure, thickness and conductivity effected in the dyeing process.

4.4.4 Blends of Fibers

In samples 13 to 16 the yarns are blends of wool with 15 or 30 percent of various synthetic fibers. There is little difference between the various blends and probably the protection is about the same as for all wool.

4.4.5 Orlon

There was sufficient heat treated orlon for exposure on only one shot. The temperatures were approximately the same as for the 9 oz. sateen OG-107.

4.4.6 Aluminized Fabrics

Possibly the most outstanding result was the protection afforded by a single layer of aluminized cotton drill, 7 oz. per sq. yd. The maximum temperatures at 15 langley's were 62° in contact and 56° spaced. The corresponding values for 9 oz. sateen are 50 to 200°C higher. Apparently the high reflectance and low transmittance are the important factors in providing this protection. When this aluminized surface was covered with a layer of orlon, with a total weight of 15.8 oz. per sq. yd. the protection was considerably less, with temperatures up to twice that for the unprotected aluminum surface. Unfortunately it does not seem possible to retain the advantage of high reflecting layers if they must be camouflaged.

4.4.7 Order of Layers and Location of Spacing

The contact side of sample 22 was the same as sample 4 with the exception that the order was reversed; i.e., the underwear was out and the 9 oz. W.R. sateen in contact with the backing. The temperatures were about the same for the two cases.

The spaced side of sample 22 was the same as sample 4 except

[REDACTED]
UNCLASSIFIED

the space was between the flannel and undershirt and the undershirt was in contact with the backing. Again the results are about the same for the two cases.

For both samples the intensity was too low to show any differences that may have existed.

4.4.8 Spacing

Previous tests as well as the current one showed that for opaque fabrics, the protection was considerably greater if the fabric were spaced from the backing. However, all the results were at a single fixed spacing of 1/4 inch. In sample 21 the spacing was 1/16 and 1/2 inch. There was a definite dependence of temperature on spacing. The values for samples 8 and 21 are listed below:

	<u>Spacing</u>			
	<u>0 (contact)</u>	<u>1/16 in.</u>	<u>1/4 in.</u>	<u>1/2 in.</u>
6 langleys	68-133	62-79	62	48
15	133-257	146-257	146-240	100-180

For the low ^{energy} intensity there is a considerable drop from contact to a very small spacing and also a continuing decrease up to 1/2 in. spacing. At the higher ^{energy level} intensity there is little difference between contact and a 1/4 in. spacing but a definite drop between 1/4 and 1/2 in.

4.4.9 Summary

The temperatures were higher for clothing fabrics on flat panels than for the corresponding ensembles on dummies. To a large extent this resulted from differences in contact between layers and between fabric and backing and to variations in the angle of incidence. To some extent the difference was due to variations in weight of fabric since the panels were not exactly like the clothing. They did not include extra thicknesses at folds, seams, plaits and pockets.

The temperatures behind the cold bar combination were approximately the same as for the cold wet fabric combination, possibly just slightly higher.

There were differences due to reflectance and fabric weight, generally in agreement with previous results and with expectations from laboratory studies. The temperatures with camouflage shades were just slightly higher than with standard shades, for both cotton and wool. The undyed fabric did not provide good protection. On the other hand, the aluminized fabric probably gave the best protection of any fabric tested

UNCLASSIFIED
[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]
UNCLASSIFIED

here previously, for a corresponding weight. The transmittance of underlying layers did not seem to have any influence on the temperature. The orlon fabric did not provide outstanding protection. Blends of wool and synthetics, at least up to 15 percent, were as good as all wool.

In a single test there was no effect of varying the order of layers nor varying the location of a single spacing between layers. There was a definite effect of increasing the spacing with a continuous decrease in temperature from 1/16 to 1/2 inch spacing.

TABLE 4.1

Fabric Samples for Panel Tests
 Fabrics are in order with First Layer Exposed, Last Layer next to Backing

Sample No.	Nomenclature	Nominal Weight oz/yd ²	Shade	Reflectance %		Transmittance %		Spec. No. or Laboratory Designation
				V	IR	V	IR	
1	Cl. ctn. Oxford, permeable " " knitted (light weight undershirt)	5.2	00-116 White	8.0	21.5	2.5	7.5	MIL-C-10859B
				69.5	78.5	34.	36.	JAN-U-797
2	Hot Dry Cl. ctn. uniform twill " " knitted (light weight undershirt)	8.2	Khaki I W/A, T-C	25.	62.	1.	12.	JAN-C-298
				69.5	78.5	34.	36.	JAN-U-797
3	Temperate Cl. ctn. wind resistant sateen Cl. wool flannel Cl. wool & ctn. knitted (winter undershirt)	9	00-107 Grey	7.	17.5	<0.5	<0.5	MIL-C-557A
				5.5	14.5	12.5	20.	MIL-C-10752 MIL-U-10211B
4	Cold Wet Cl. ctn. wind resistant sateen Cl. Mohair, frieze Cl. rayon, rip-stop Cl. wool, flannel Cl. ctn. & wool, knitted (winter undershirt)	9	00-107 White	7.	17.5	<0.5	<0.5	MIL-C-557A
				51.5	69.5	15.	21.5	MIL-C-10751 MIL-C-10772a MIL-C-10752 MIL-U-10211b
5	Cold Dry Cl. ctn. warp, nylon filled oxford	5	00-107 Grey	7.5	16.	<0.5	2.	MIL-C-10829
				5.5	14.5	12.5	20	

UNCLASSIFIED

UNCLASSIFIED

UNCLASSIFIED

TABLE 4.1 (cont'd)

Fabric Samples for Panel Tests

Fabrics are in order with First Layer Exposed, Last Layer next to Backing

Sample No.	Nomenclature	Nominal Weight oz/yd ²	Shade	Reflectance %		Transmittance %		Spec. No. or Laboratory Designation
				V	IR	V	IR	
6	Cl. mohair, frieze	17	White	51.5	69.5	15.	21.5	MIL-C-10751
	Cl. rayon, rip stop	1.8	OD-7	12.5	67.5	7.	32.5	MIL-C-10772A
	Cl. ctn. wind resistant, sateen	9	OG-107	6.5	17.5		0.5	MIL-C-557A
	Cl. Mohair, Frieze	17	White	51.5	69.5	15.	21.5	MIL-C-10751
	Cl. rayon, rip stop	1.8	OD-7	12.5	67.5	7.	32.5	MIL-C-10772A
	Cl. wool, flannel	10.3	OG-106					MIL-C-10752
	Cl. wool & ctn. knitted (winter undershirt)	10.5 72	Grey	55.	75.	12.5	20	MIL-U-10211B
	Cl. ctn. wind resistant, sateen	9	OG-107	7.	17.5	<0.5	<0.5	MIL-C-557A
	Cl. mohair, frieze	17	White	51.5	69.5	15.	21.5	MIL-C-10751
	Cl. rayon, rip stop	1.8	OD-7	12.5	67.5	7.	32.5	MIL-C-10772A
7	Cl. ctn. wind resistant, sateen	9	OG-107	6.5	17.5		0.5	MIL-C-557A
	Cl. mohair, frieze	17	White	51.5	69.5	15.	21.5	MIL-C-10751
	Cl. rayon, rip stop	1.8	OD-7	12.5	67.5	7.	32.5	MIL-C-10772A
	Cl. wool, flannel	10.3	OG-106	5.5	14.5			MIL-C-10752
	Cl. wool & ctn. knitted (winter under shirt)	10.5	Grey	55.	75.	12.5	20	MIL-U-10211B
	Cl. ctn. wind resistant, sateen (Cold bar)	9	OG-107	7.	17.5	<0.5	<0.5	MIL-C-557A
	Plastic, expanded, unicellular, elastomeric (Insulite) (cold bar)	31a 40						MIL-P-12420

a. About 9/32 in. thick, density about 5.1 lbs/ft³.

UNCLASSIFIED

TABLE 4.1 (cont'd)

Fabric Samples for Panel Tests
 Fabrics are in order with First Layer Exposed, Last Layer next to Backing

Sample No.	Nomenclature	Nominal Weight oz/yd ²	Shade		Reflectance %		Transmittance %		Spec. No. of Laboratory Designation
			OG-107	White	V	IR	V	IR	
8	Cl. ctn. wind resistant sateen	9	OG-107	White	7.	17.5	<0.5	<0.5	MIL-C-557A
9) 9a)	Cl. ctn. wind resistant sateen	9	OD-7	White	9.5	26.0	<0.5	<0.5	MIL-C-557A
10	Cl. ctn. wind resistant sateen	9	White	White	69.	82.5	12.5	18	MIL-C-557A
11	Cl. ctn. wind resistant sateen	9	OG-107	White	7.	17.5	<0.5	<0.5	MIL-C-557A
	Cl. mohair, frieze	$\frac{17}{26}$	White	White	51.5	69.5	15.	21.5	MIL-C-10751
12	Cl. ctn. wind resistant sateen	9	OG-107	White	6.5	17.5	<0.5	<0.5	MIL-C-557A
	Cl. Mohair, frieze	$\frac{17}{26}$	OD-7	White	8.5	57.5	0.5	12.5	MIL-C-10751
13	Cl. wool, serge	11.6	OG-108	White	5.5	14.5		0.5	J.P. Stevens
14	Cl. wool, serge	11.6	OD-33	White	12.	45.		12.5	MIL-C-11305 QMC. Livingston Pc. 7412
15	Cl. 70% wool, 30% dacron	11.6	OD-33	White	8.0	44.5			
16	Cl. 85% wool, 15% nylon	11.6	OG-108	White	6.5	30.			

UNCLASSIFIED

UNCLASSIFIED

TABLE 4.1 (cont'd)

Fabric Samples for Panel Tests
 Fabrics are in order with First Layer Exposed, Last Layer next to Backing

Sample No.	Nomenclature	Nominal Weight oz/yd ²	Shade	Reflectance %		Transmittance %		Spec. No. or Laboratory Designation
				V	IR	V	IR	
17	Cl. 85% wool, 15% dynel	11.6	OD-33	8.5	46.	8.5	<0.5	Johns-Manville
18	Cl. orlon, spun, heat treated	8.3	black	4.	3.5	<0.5	<0.5	Johns-Manville
19	Cl. ctn. twill, aluminized	7.0	alum.	74.	74.	1.	2.5	National Research Corp.
20	Cl. orlon, spun, heat treated	8.3	black	4.	3.5	<0.5	<0.5	Johns-Manville
	Cl. ctn. twill, aluminized	7.0	alum.	74.	74.	1.	2.5	National Research Corp.
21	Spacing sample - 1/16 & 1/2 in. Cl. ctn. wind resistant sateen 9		OG-107	7.	17.5	<0.5	<0.5	MIL-C-557A
22	Composite layer sample a. space between shirt & undershirt, undershirt in contact cl. ctn. wind resistant	9	OG-107	7.	17.5	<0.5	<0.5	MIL-C-557A
	cl. mohair, frieze	8.4	White	51.5	69.5	15.	21.5	MIL-C-10751
	cl. rayon, rip stop	1.8	OD-7	12.5	67.5	7.	32.5	MIL-C-10772A
	cl. wool, flannel 1/4 in. space	10.3	OG-108	5.5	14.5			MIL-C-10752
	Cl. wool & ctn. under-wear, knitted (winter undershirt)	10.5	Grey	55.	75.	12.5	20.0	MIL-U-10211B

TABLE 4.1 (cont'd)

Fabric Samples for Panel Tests
Fabrics are in order with First Layer Exposed, Last Layer next to Backing

Sample No.	Nomenclature b. Contact	Nominal Weight oz/yd ²	Reflectance %		Transmittance		Spec. No. or Laboratory Designation
			V	IR	V	IR	
	Same fabrics in reverse order, no space						Same
		40					

[REDACTED] GY

[REDACTED]

UNCLASSIFIED

TABLE 4.2

Damage to Fabrics on Panels
Damage Code in Section 4.4

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Damage Rating			
				Shot 6 10 Langley's C	Shot 6 S	Shot 8 13 Langley's C	Shot 8 S
1	Cotton, permeable Light weight undershirt	5.2 3	OG-116 White	997 310	999 310	--9 511	--9 311
2	Cotton, uniform twill Light weight undershirt	8.2 3	Khaki 1 White			731 310	731 310
3	Cotton, WR sateen Wool flannel Winter undershirt	9 10.3 10.5	OG-107 OG-108 Grey	731 310 100	751 310 100	999 300 100	999 300 100
4	Cotton, WR Sateen Mohair frieze Rayon lining Wool flannel Winter undershirt	9 17 1.8 10.3 10.5	OG-107 White OD-7 OG-108 Grey	733 610 000 000 000	733 510 000 000 000	999 510 000 000 000	--9 510 000 000 000
5	Cotton warp nylon filling oxford Mohair frieze Rayon lining Cotton, WR sateen Mohair frieze Rayon lining Wool flannel Winter undershirt	5 17 1.8 9 17 1.8 10.3 10.5	OG-107 White OD-7 OG-107 White OD-7 OG-108 Grey			--9 510 000 000 000 000 000	--9 510 000 000 000 000 000
6	Cotton, WR sateen Mohair frieze Rayon lining	9 17 1.8	OG-107 White OD-7	711 410 000	713 310 000		

UNCLASSIFIED

TABLE 4.2 (cont'd)

Damage to Fabrics on Panels
Damage Code in Section 4.4

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Damage Rating		
				Shot 6 10 langley's C	Shot 6 13 langley's C	Shot 8 13 langley's S
	Cotton, WR sateen	9	OG-107	000	000	000
	Mohair frieze	17	White	000	000	000
	Rayon lining	1.8	OD-7	000	000	000
	Wool flannel	10.3	OG-108	000	000	000
	Winter undershirt	10.5	Grey	000	000	000
7	Cotton, WR sateen Insulite	9	OG-107	731 300	731 300	999 300
8	Cotton, WR sateen	9	OG-107	731	731	997
9	Cotton, WR sateen	9	OD-7	511	531	976
9a	Cotton, WR sateen	9	OD-7			955
10	Cotton, WR sateen	9	White			000
11	Cotton, WR sateen Mohair Frieze	9 17	OG-107 White	731 310	731 310	
12	Cotton, WR sateen Mohair Frieze	9 17	OG-107 OG-108	731 500	751 500	
13	Wool serge	11.6	OG-108	701	701	907
14	Wool serge	11.6	OD-33	900	700	905
15	70% wool, 30% dacron, serge	11.6	OD-33	701	701	955

TABLE 4.2 (cont'd)

Damage to Fabrics on Panels
Damage Code in Section 4.4

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Damage Rating	
				Shot 6	Shot 8
16	85% wool, 15% nylon serge	11.6	OG-108	10 lengleys C	13 lengleys S 911 912
17	95% wool, 5% dynel serge	11.6	OD-33		903 903
18	Orlon, heat treated	8.3	Black	501	500
19	Cotton twill, aluminized	7.0	Alum.	100	100
20	Orlon, heat treated	8.3	Black	500	500
	Cotton twill, aluminized	7.0	Alum.	100	100
21	Cotton WR sateen, 1/16 in. space				
	1/2 in. space				
22	<u>Contact</u>				
	Winter underwear	10.5	Grey	100	
	Wool flannel	10.3	OG-108	000	
	Rayon lining	1.8	OD-7	000	
	Mohair frieze	8.4	White	000	
	Cotton WR sateen	9.	OG-107	000	
	<u>Spaced</u>				
	Cotton WR sateen	9.	OG-107		751
	Mohair Frieze	8.4	White		310
	Rayon lining	1.8	OD-7		000
	Wool flannel	10.3	OG-108		000
	1/4 in. space				
	Winter underwear, in contact	10.5	Grey		000

UNCLASSIFIED

UNCLASSIFIED

-9
-9

TABLE 4.3

Temperatures Behind Fabrics on Panels

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Temperature, °C						
				4 langleya		Shot 6				
				C	S	C	S			
1	Cotton, permeable Light weight undershirt	$\frac{3}{9}$	OD-7 White	68	106	62	133	223	74	118
2	Cotton, uniform twill Lightweight undershirt	$\frac{8.2}{11}$	Khaki 1 White							
3	Cotton, WR sateen Wool flannel Winter undershirt	$\frac{9}{10.3}$ $\frac{10.5}{30}$	OG-107 OG-108 Grey	56	62	56	62	56	68	56
4	Cotton, WR sateen Mohair frieze Rayon lining Wool, flannel Winter undershirt	$\frac{9}{17}$ $\frac{1.8}{10.3}$ $\frac{10.5}{49}$	OG-107 White OD-7 OG-108 Grey	56	48	56	56	56	56	56
5	Cotton warp, nylon filling oxford Mohair frieze Rayon lining Cotton, WR sateen Mohair frieze Rayon lining Wool flannel Winter undershirt	$\frac{5}{17}$ $\frac{1.8}{9}$ $\frac{17}{10.3}$ $\frac{10.5}{72}$	OG-108 White OD-7 OG-107 White OD-7 OG-108 Grey							

UNCLASSIFIED

UNCLASSIFIED

TABLE 4.3 (cont'd)

Temperatures Behind Fabrics on Panels

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Temperature, °C			
				4 langley's		10 langley's	
				C	S	C	S
6	Cotton, WR sateen	9	OG-107				
	Mohair frieze	17					
	Rayon lining	1.8					
	Cotton, WR sateen	9					
	Mohair frieze	17		48	56	48	48
	Rayon lining	1.8					
	Wool flannel	10.3					
	Winter undershirt	10.5					
			76				
	7	Cotton, WR sateen	9	OG-107	48	56	62
	Insulite						
8	Cotton, WR sateen	9	OG-107	79	106	62	146 257 146 257
9	Cotton, WR sateen	9	OD-7	68	92	62	133 223 100 175
9a	Cotton, WR, sateen	9	OD-7				
10	Cotton, WR sateen	9	White				
11	Cotton, WR sateen	9	OG-107	48	56	56	62 62
	Mohair frieze	8.4 17	White				
12	Cotton, WR sateen	9	OG-107	56	62	62	68 62
	Mohair frieze	8.4 17	OG-108				

UNCLASSIFIED

UNCLASSIFIED

TABLE 4.3 (cont'd)

Temperatures Behind Fabrics on Panels

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Temperature, °C							
				4 langley's		10 langley's					
			C	S	C	S	Shot 6				
13	Wool, serge	11.6	OG-108	68	79	62	68	100	180	100	146
14	Wool, serge	11.6	OD-33	68	84	62	74	106	157	100	146
15	70% wool, 30% dacron, serge	11.6	OD-33	62	79	62	74	100	146	100	106
16	85% wool, 15% nylon, serge	11.6	OG-108								
17	85% wool, 15% dynel, serge	11.6	OD-33								
18	Orlon, heat treated	8.3	Black	74	92	62	68	146	257	146	223
19	Cotton, twill, aluminized	7.0	Alum.	48	48	48	48	48	62	48	56
20	Orlon, heat treated Cotton twill, aluminized	8.3 7.0	Black Alum.	68	106	62	62	84	180	62	68
21	Cotton, WR sateen, 1/16" space 1/2" space	9 9	OG-108 OG-108								
22	Composite Contact										
	Winter underwear	10.5	Grey								
	Wool, flannel	10.3	OG-108								
	Rayon, lining	1.8	OD-7	48	62						48
	Mohair frieze	8.4	White								
	Cotton, WR sateen	9	OG-107								
		<u>9</u>									
		40									

TABLE 4.3 (cont'd)

Temperatures Behind Fabrics on Panels

Sample No.	Description	Nominal Weight oz/yd ²	Shade	Temperature, °C	
				Shot 8	Shot 8
9				5 Langley's C	13 Langley's C
9a				74 105 56 62	146 257 146 257
10				68 106 48 56	157 257 157 257
11				79 118 74 146	180 257 161 257
12					
13				68 84 48 62	100 180 100 146
14				74 92 62 92	146 180 118 180
15				74 84 50 79	146 223 146 161
16				68 92 56 79	118 223 118 157
17				68 84 56 74	118 223 100 146
18					
19					
20					
21	Cotton, WR Sateen, 1/16" space	9	0G-108	62 79	146 257
22	1/2" space	9	0G-108	48	100 205

[REDACTED] UNCLASSIFIED

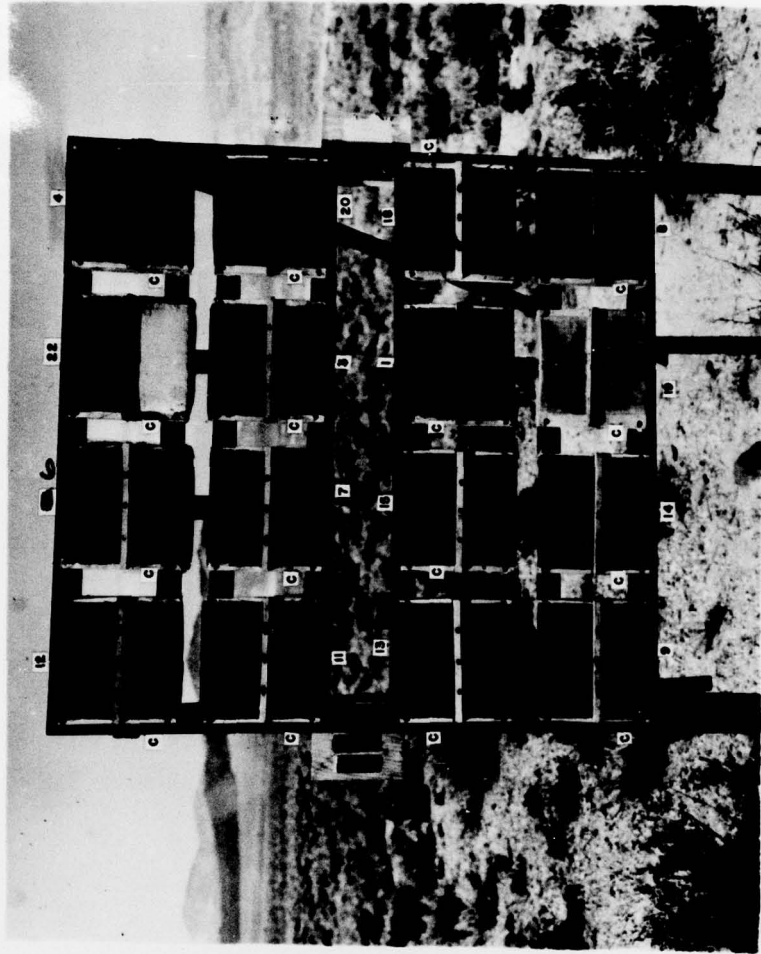


Fig. 4.1 Fabrics on Panels - Shot 6 - 1-1/2 Miles

[REDACTED]
UNCLASSIFIED

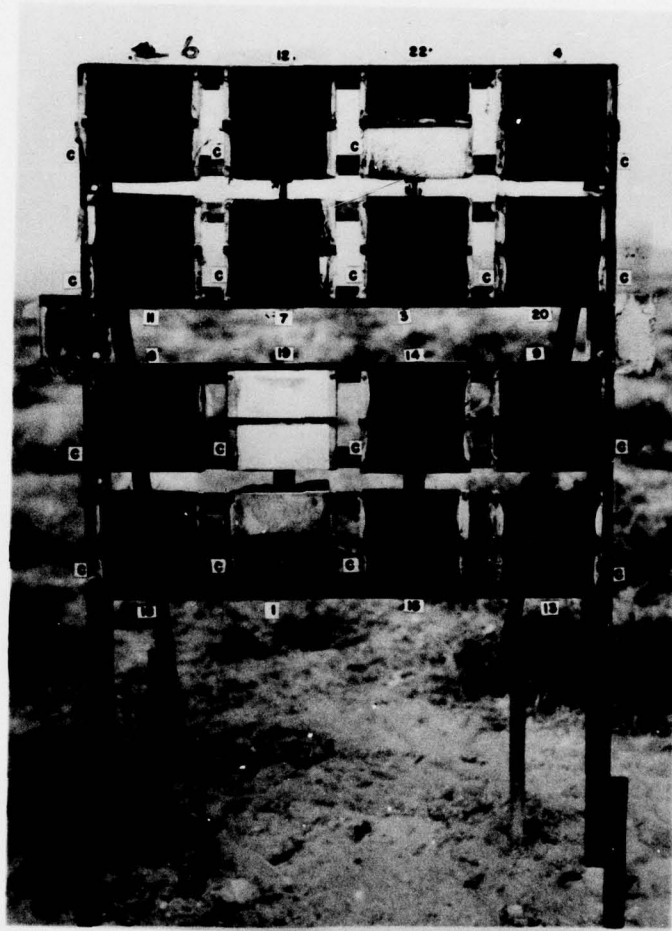


Fig. 4.2 Fabrics on Panels, Shot 6,1 Mile

- 69 - UNCLASSIFIED

[REDACTED]
[REDACTED]
ACT 10/6

[REDACTED] UNCLASSIFIED

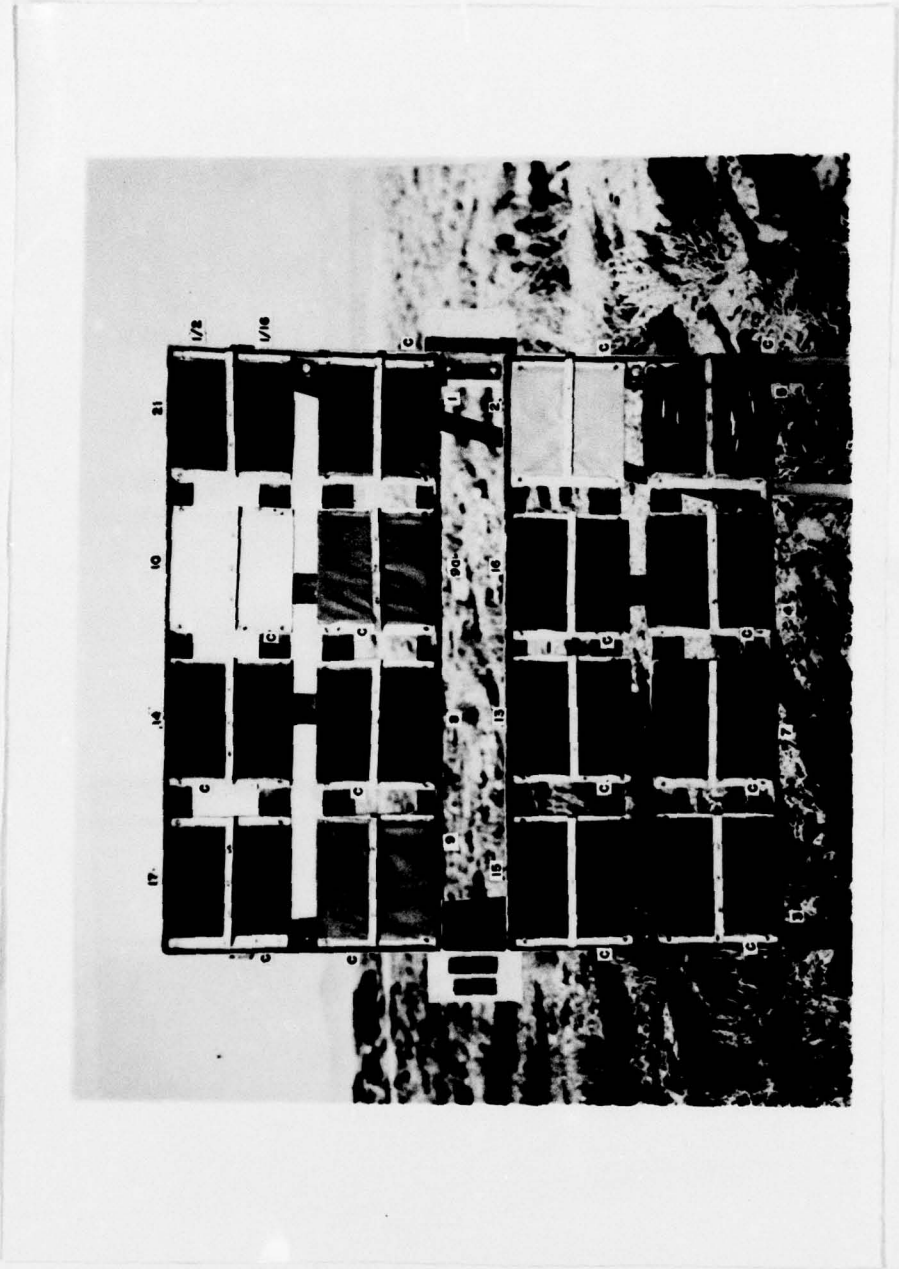


Fig. 4.3 Fabrics on Panels Shot. 6, 1-1/2 Miles

[REDACTED] [REDACTED] TA
[REDACTED] ENERGY

[REDACTED]

UNCLASSIFIED

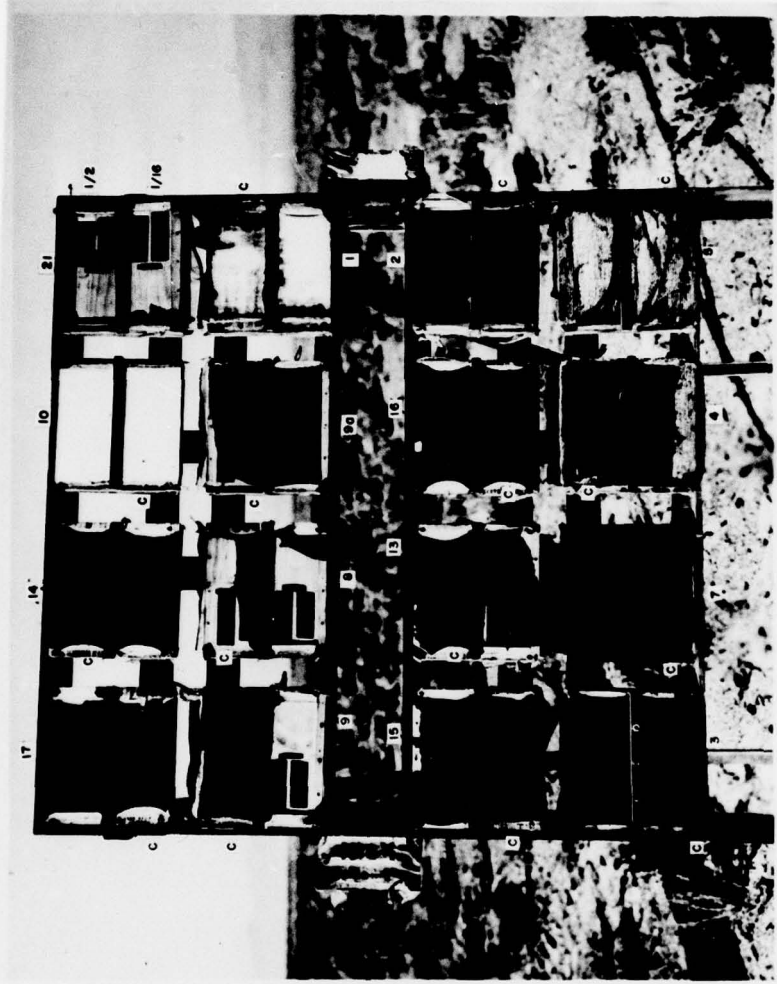


Fig. 4.4 Fabrics on Panels. Shot 8, 1 Mile

[REDACTED]

[REDACTED]
ACT 2014

[REDACTED]

UNCLASSIFIED

CHAPTER 5

PROTECTIVE CREAM

5.1 GENERAL

The QM Cream, Protective, Flash Burn, described in Purchase Description, 16 January 1952, was tested in 3 thicknesses, from a very thin layer to 1/16 inch thick. The protective value was measured with the temperature indicators described in Section 2.3. Samples were exposed at about 1 and 1-1/2 miles from ground zero for both shots.

5.2 SAMPLES

The indicators were mounted face down on the surface of 1/2 inch plywood and held in place with adhesive tape along the edges. They were covered with an .001 inch vinyl film to protect the indicators from solvents in the cream, and the cream was applied over the film. The film was folded over the edge of the plywood but otherwise was not adhered to the indicators or backing. An attempt was made to control the thickness of the cream by using spacers in the application. For the two thicker applications, an excess of material was applied and scraped off with a straight edge riding on 1/16 and 1/32 in. flat spacers. The thinner sample was applied without spacers and the thickness was less definite and less uniform.

The samples were prepared as late as possible on the day before the shot but even so, this was at least 12 hours before exposure. They dried out considerably in that time but no measure was made of the moisture content.

The reflectance of this material was measured, freshly prepared and after drying overnight the curve in Fig. 2.1 is the average. The average reflectance was about 37 percent in the visible and 32 percent in the near infra red region. The difference between them was about 1.5 percent throughout the range. In the visible and near infra red regions the transmittance is negligible.

The density of the cream is about 1.55 grams per cubic centimeter and as a thin film the loss in weight may be 2 to 5 percent in 24 hours. A density of 1.55 grams per cubic centimeter is equivalent to weights of 71, 36, and 18 ounces per sq. yd. for 1/16, 1/32, and 1/64 inch films.

5.3 DAMAGE TO THE CREAM

Below 5 langleys there was no visible effect on the cream. At ¹⁰ ~~12~~

UNCLASSIFIED

to 13 langleys there was evidence of small bubbles but no other damage.

5.4 PROTECTIVE VALUE

The protective value of the cream as shown by the temperature indicators is given in Table 5.1. Here the protection is the combined effect of cream and the .001 in. vinyl film.

The cream provides considerable protection, the indicators covered with only a .001 in. vinyl sheet were badly charred or completely gone with indicated temperatures above 257°C. With various thicknesses of cream the temperature ranged from 205 to 48°C.

At first sight there is an apparent discrepancy between the two results at 5 and 13 langleys on Shot 8 with temperatures of 62°C at 5 and 48°C at 13 langleys. However, the thickness was greater for the latter, .05 in. compared to .04 in. The protection increases rapidly with thickness and apparently the effect was great enough to cause this difference in temperatures.

It is difficult to express the results in terms of skin burns. If the tentative figure of 141°C from fabric studies is taken here, then possibly 24 burns would have occurred at 4 and 5 langleys with 1/64 in. of cream. However, this exposure should barely produce such burns with no protection and obviously from the temperatures shown there was considerable protection. On the other hand there would have been no burns at 10 or 15 langleys with 1/16 inch of cream and there would certainly have been severe burns on unprotected skin.

Possibly some additional idea of the protective value can be obtained from other data on unprotected indicators. At about 4 miles from ground zero, the calculated exposures were .6 and .8 langleys for Shots 6 and 8. Indicators with no protection and with a .001 in. vinyl sheet and a .003 in. transparent adhesive tape gave the temperatures shown in Table 5.2. In this case the transparent cover reduced the temperatures considerably, probably mainly by reflecting some of the radiation. The protective value of the films where used in connection with the face cream was likely less and accordingly a temperature just less than 74-92°C can be used for comparison with the results in Table 4.2. Comparisons of this kind are somewhat risky unless the mechanisms of heat transfer are understood and can give only approximate answers. With that uncertainty in mind, it seems that conditions will be just about the same behind just slightly more than 1/32 in. of face cream at 4 to 5 langleys as with no face cream at .6 to .8 langleys.

- 73 - UNCLASSIFIED

ATOMIC ENERGY

1957-10-6

TABLE 5.1

Protection Afforded by QM Face Cream

Estimated, as Applied	Thickness, in. Measured after Return to Lab.	Temperature, °C			
		Shot 6		Shot 8	
		4 lang.	10 lang.	5 lang.	13 lang.
0	0	>257 ^a	>257 ^b	>257 ^a	>257 ^b
1/64	.01	100	161	118	205
1/32	.02	68	92	79	175
1/16	.04	<48	48 ^c	62	<48 ^d

- a Paper of indicators very badly charred.
- b Indicators completely gone.
- c Thickness .06 in.
- d Thickness .05 in.

TABLE 5.2

Temperature of Exposed Indicators

	Temperature, °C	
	Shot 6 .6 langley	Shot 8 .8 langley
No protection	74-92	74 ^a -- 92 ^a
Under .001 in. vinyl sheet	62-74	
Under transparent adhesive tape, .003 in. total thickness		48 -- 62

- a. Although the range is the same, probably slightly higher temperature than the corresponding indicator of Shot 6.

[REDACTED]

UNCLASSIFIED

CHAPTER 6

PACKAGING

6.1 GENERAL

Three wood boxes were exposed, one each at 2910, 4110 and 5810 feet from ground zero for Shot 8. Temperatures inside were measured with the indicators described in Section 2.3.

6.2 SAMPLES AND EXPOSURE

The boxes were 26 in. x 26 in. x 26 in., roughly constructed of 3/4 inch thick pine boards. A 3/4 in. board was fastened in a vertical position across the box at the center.

Indicators were mounted on the center board, face down and held in place with adhesive tape at the edges. The indicators were about 5 inches from the bottom of the box on the side of the board facing ground zero. The boxes were placed flat on the ground with the front edges normal to the beam. They were not fastened down.

The results are summarized in Table 6.1. These results are difficult to understand. They appear to be in reverse order with the highest temperature at the greatest distance. However, this effect was noticed at the time, and the sample identification was carefully checked. There is little chance that the data as listed do not refer to the correct locations.

It seems likely that in this case there was obscuration by dust, possibly from the shockwave but also possibly from the popcorn-like bursting of soil particles under the action of thermal radiation⁵ which presumably could happen at these ~~intensities~~ ^{EXPOSURES} since it occurs in the laboratory at 11 langleys. The boxes were on the ground, with the highest point only 2 feet above the surface and dust could very well have reduced these intensities without influencing the radiation on fabrics higher off the ground.

If this analysis is correct then the temperatures at 2910 and 4110 feet are too low by a considerable amount. The result at 5810 feet is also uncertain; it represents a minimum figure. Even if the temperatures at that distance without dust should be as low as 56 to 74°C, the corresponding temperatures at 4110 and 2910 feet would be considerably higher. The radiation intensities were roughly 2 and 4 times as great but it is difficult to estimate the difference in the resulting temperatures.

[REDACTED]
UNCLASSIFIED

TABLE 6.1

Results of Packaging Test

<u>Distance from Ground Zero, Ft.</u>	<u>Radiant Exposure langleys</u>	<u>Damage to Box</u>		<u>Temperature Inside Box, °C</u>
		<u>Thermal</u>	<u>Blast</u>	
2910	40	Side facing the explosion charred deeply, 1/16 to 1/8 in. deep	One board blown off bottom of box. Box moved 65 ft.	<48
4110	20	Side of box facing explosion charred	One board blown off box. Box moved 30 ft.	48
5810	10	Side of box facing the explosion slightly scorched	Box turned over	56-74

UNCLASSIFIED
[REDACTED]
[REDACTED]
[REDACTED]

[REDACTED]

UNCLASSIFIED

BIBLIOGRAPHY

1. Protective Value and Ignition Hazards of Textile Materials Exposed to Thermal Radiation, Operation Buster, Project 2.4a, June 1952. J. M. Davies and Major A. H. Parthum, Jr., QMC.
2. Operation Ranger, June 1953. J. M. Davies, QMC.
3. Exercise Desert Rock IV, April-June 1952. Test Director's Report.
4. Letter, Armed Forces Special Weapons Project, SWPEF-1, 400.112 2 January 1953.
5. Thermal & Optical Properties of Nevada Sand, Naval Material Laboratory, Project C-5046-3, Part 19, Final Report, May 1952. I. J. Bates, J. A. Carter and T. I. Monahan.
6. Letter, Dr. Herman Pearse to Dr. R. G. H. Siu, 28 October 1952.

UNCLASSIFIED

[REDACTED]

[REDACTED]

[REDACTED]