

AD-A079 351

AMERICAN UNIV WASHINGTON DC DEPT OF CHEMISTRY

F/B 11/6

THE CHEMICAL NATURE OF ALUMINUM CORROSION. I. ACTIVATION OF ALU--ETC(U)

NOV 79 K SOTOUDEN, R T FOLEY, B F BROWN

N00014-75-C-0799

UNCLASSIFIED

TR-10

NL

[]
AD
ADDRESS



END
DATE
FILMED
2-80

DOC

12
ADA 079351


**The Chemical Nature of Aluminum Corrosion:
I. Activation of Aluminum Surfaces by
Aluminum Salts**

II
Technical Report No. 10


Department of Chemistry
The American University
Washington, D.C. 20016

By:
K. Sotoudeh, R.T. Foley and B.F. Brown
November 1979

To:
Office of Naval Research
Contract N00014-75-C-0799
NR 036-106

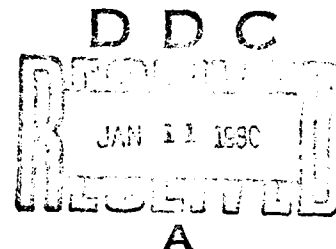

DDC FILE COPY

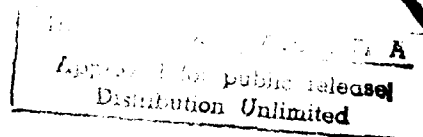

Reproduction in whole or in part is permitted for any
purpose of the United States Government.

This work was sponsored by the Metallurgy and
Ceramics Program of the Office of Naval Research.

80 1-10 019

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
(1) Technical Report No. 10		(9)
4. TITLE (and Subtitle) The Chemical Nature of Aluminum Corrosion. I. Activation of Aluminum Surfaces by Aluminum Salts.		5. TYPE OF REPORT & PERIOD COVERED Technical Progress Report.
6. AUTHOR(s)		7. CONTRACT OR GRANT NUMBER(s)
(10) K. Sotoudeh, R. T. Foley and B. F. Brown		(15) N 00014-75-C-0799 NR 036-106
9. PERFORMING ORGANIZATION NAME AND ADDRESS The American University Massachusetts and Nebraska Avenues, NW Washington, DC 20016		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS Metallurgy and Ceramics Program Office of Naval Research Arlington, VA 22217		12. REPORT DATE November 1979
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) (12) 20		13. NUMBER OF PAGES 13
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Distribution of this document is unlimited. (14) TR-10		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Aluminum, corrosion, pitting, stress corrosion cracking		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The activation of aluminum surfaces (alloys 1199-H14 and 7075-T6) by solutions of $Al(NO_3)_3$, $AlBr_3$, $AlCl_3$, $Al_2(SO_4)_3$, $Al(ClO_4)_3$, AlI_3 and $NaCl$ of various concentrations has been measured. Experiments were also conducted in saturated solutions of aluminum acetate, benzoate, phosphate, chromate and fluoride. The dissolution rate of the alloys varies considerably with the salt, the nitrate and iodide being most aggressive. The corrosion rate in sulfate solutions is much less than the rate in bromide, chloride, or perchlorate. The pH of the various salt solutions is not the determining parameter but for a given salt		


DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

Unclassified 387562
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. (AlCl₃) the corrosion rate increases with decrease in pH. The experiments definitely demonstrate that the activation effect is not restricted to aluminum chloride and suggests a strong chemical effect in the pitting and stress cracking mechanism. ↙

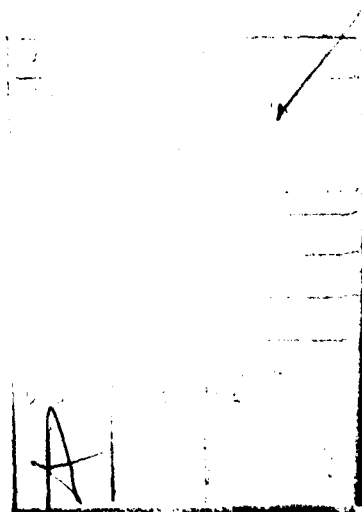

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

THE CHEMICAL NATURE OF ALUMINUM CORROSION: I ACTIVATION
OF ALUMINUM SURFACES BY ALUMINUM SALTS

K. Sotoudeh, R. T. Foley and B. F. Brown

Department of Chemistry
The American University
Washington, D.C. 20016

Aluminum and its alloys are passive unless they are made active by either chemical environments or mechanical actions or by a combination of the two. Although water vapor has been shown in laboratory experiments to be capable of propagating stress corrosion cracks (which indicates a locally active state), it is known from both service experience and laboratory experiments on stress corrosion cracking (to be reported subsequently in this series) that there are effects involving ions other than those of water. It is also known from laboratory experiments that the corrodent in localized forms of corrosion (such as pitting and stress corrosion cracking) is chemically different from the bulk environment, though whether this change is a cause or rather a result of the localized corrosion has not been established.

It is generally recognized that the pH of the solution in a growing pit on an aluminum alloy or in a crack on a stress-cracking specimen of an aluminum alloy is approximately 3.5 and there appears to be a relatively high concentration of Al^{+++} . Experiments by Rosenfeld and Marshakov¹, Brown, et al.², Marek, et al.³, Davis⁴, and Hagyard and Santhiapillai⁵ support this conclusion. The analytical studies on the nature of local corrodents by Brown, et al., by Marek, et al. and by Davis were conducted on small quantities of corrodent, with attendant uncertainties, and they involved only chloride as

an anion (other than OH^-). Indeed, most of the experimental work in this field has been done in chloride solution and thus an attempt has been made to relate this corrosion to the hydrolysis of aluminum chloride. Almost without exception the thinking has been focused on aluminum chloride and as a result a complete understanding of the pitting mechanism or the stress cracking mechanism has not been realized. The fact is that, aluminum pits and cracks in a number of (non-chloride) environments.

The objective of this work was to measure the corrosion rate of aluminum alloy 1199 and alloy 7075 in various aluminum salt solutions to determine the ability of these various salts to activate the aluminum surface. The longer range intent is to relate this specific corrosion reaction to the initiation of pitting and the stress cracking process.

EXPERIMENTAL

The experimental work reported here consisted of immersion tests with two aluminum alloys, alloy 1199-H14 and alloy 7075-T6. Samples $38 \times 26 \times 0.81$ mm were cleaned in the conventional manner. The strip was immersed in NaOH solution (5g/100ml) at $70^\circ\text{--}80^\circ\text{C}$ for one minute, rinsed thoroughly, dipped in HNO_3 (1:3) for one minute at room temperature, and thoroughly rinsed in distilled water and acetone. Samples were immersed in triplicate in solutions of $\text{Al}(\text{NO}_3)_3$, AlBr_3 , AlCl_3 , $\text{Al}_2(\text{SO}_4)_3$, $\text{Al}(\text{ClO}_4)_3$, AlI_3 and NaCl of various concentrations as well as in saturated solutions of aluminum acetate, aluminum benzoate, aluminum phosphate, aluminum chromate and aluminum fluoride. These samples were immersed for 7 to 9 day periods at room temperature, $23^\circ \pm 2^\circ\text{C}$. Following exposures, the corrosion products were removed with a stripping solution of 20 g of chromic acid and 32.25 ml of 85% phosphoric acid/liter. The weight loss reported was the difference

in weight of the sample before the test and that after the stripping. The latter was corrected with the weight loss of an uncorroded metal specimen in the stripping solution.

RESULTS

The weight losses for alloy 1199 immersed in 0.1M solutions of aluminum nitrate, bromide, chloride, sulfate, perchlorate and iodide are given in Table I. The activating effect of the nitrate and iodide is approximately three times that of the bromide, chloride and perchlorate, the sulfate one-half. This order is approximately followed in 0.2N solutions in a 7-day experiment reported in Table II. In neither set of experiments is there a correlation between corrosion rate and pH. The pH of these solutions fell in the 3.0-4.0 range with the exception of the aluminum perchlorate solution which had a pH of 2.6-2.7.

Dissolution rates for alloy 7075 in 0.5M solutions of the salts (Table III) were appreciably higher. Aluminum iodide produced a very high corrosion rate as did the nitrate and chloride solutions. The bromide and perchlorate effects were about one-third of the latter and the sulfate solution an order of magnitude lower. Again, the pH of the solution was not a significant factor.

A number of aluminum salts, mainly those formed from weak acids, were used as saturated solutions. These included aluminum acetate, benzoate, phosphate, chromate, and fluoride.

The weight losses exhibited by samples of 1199 in these saturated solutions over a 7 to 9 day period are tabulated in Table IV. Chromate and phosphate solutions gave very little corrosion but the acetate and benzoate gave low but appreciable corrosion rates. The coupons immersed in aluminum

TABLE I

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN 0.1M SOLUTIONS
OF VARIOUS ALUMINUM SALT SOLUTIONS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm ²)
$\text{Al}(\text{NO}_3)_3$	7	3.30	1.69
	8	3.33	1.22
AlBr_3	7	3.76	0.60
	9	3.64	0.79
AlCl_3	7	3.23	0.58
	9	3.28	0.80
$\text{Al}_2(\text{SO}_4)_3$	7	3.40	0.33
	8	3.28	0.42
$\text{Al}(\text{ClO}_4)_3$	7	2.60	0.60
	9	2.60	0.72
AlI_3	7	3.62	1.83

TABLE II

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN 0.2N SOLUTIONS
OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm ²)
$\text{Al}(\text{NO}_3)_3$	7	3.32	1.79
AlBr_3	7	3.68	0.74
AlCl_3	7	3.26	0.53
$\text{Al}_2(\text{SO}_4)_3$	7	3.46	0.27
$\text{Al}(\text{ClO}_4)_3$	7	2.70	0.65
AlI_3	7	3.77	1.16

TABLE III

WEIGHT LOSS OF ALUMINUM ALLOY 7075 IN 0.5M SOLUTIONS
OF ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm ²)
Al(NO ₃) ₃	7	2.63	10.6
	7	2.60	11.2
AlBr ₃	7	3.36	3.04
	10	2.94	7.07
AlCl ₃	7	2.66	9.69
	7	2.53	9.66
Al ₂ (SO ₄) ₃	7	2.90	0.83
	7	2.81	0.97
Al(ClO ₄) ₃	7	1.32	3.17
	7	1.10	4.82
AlI ₃	7	3.49	44.9
	7	3.30	51.6

TABLE IV

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN SATURATED
SOLUTIONS OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm ²)
Al(CH ₃ COO) ₃	7	4.78	0.22
	9	4.92	0.10
	7	4.53	0.16
Al(C ₆ H ₅ COO) ₃	7	3.32	0.15
	9	3.31	0.17
	7	3.54	0.17
Al PO ₄	7	3.00	0.07
	8	2.84	0.09
	7	3.39	0.01
Al(CrO ₄) ₃	7	3.49	0.005
	8	3.12	0.03
	7	3.37	0.005
AlF ₃	7	5.30	(+0.22)
	8	5.05	(+0.23)
	7	5.22	(+0.56)

fluoride solution gave a weight increase indicating that the standard stripping solution did not remove the precipitated corrosion product. Again, there was no correlation between the corrosion rate and pH of the solution. Similar results were obtained with alloy 7075 (Table V), with the exception that the rate in aluminum acetate solution at a pH, 4.7-4.9, was higher than the other solutions.

For a single salt, aluminum chloride, initially at 0.5N concentration, the corrosion rate varies with pH. This effect is shown in Table VI wherein the dissolution rate drops appreciably in going from a pH of 2.0 to 4.5.

The unexpected results obtained with aluminum nitrate, chloride, and sulfate suggested performing experiments wherein the salts were compared at approximately equivalent activity. The comparison, of necessity, was rather rough because the activity coefficients for these salts over a range of concentrations, particularly in dilute solutions, are not available. To approximate equivalent activities, solutions 0.69M in $Al_2(SO_4)_3$, 0.014M in $AlCl_3$, and 0.020M in $AlNO_3$ were compared. However, the order of activation was still the same for the three salts (Table VII).

DISCUSSION

The idea that aluminum surfaces may be activated by aluminum chloride has been advanced by several other investigators. The "autocatalytic" nature of aluminum pitting seems to have been first suggested by Edeleanu and Evans⁶ but explored in more detail by Hagyard and Santhiapillai⁵. The latter investigators measured the pH and electrode potential inside an artificial pit on an aluminum electrode undergoing corrosion by short circuit to a graphite cathode in a solution 0.0141M in chloride. The pH in the artificial pit ranged from a minimum of 3.18 to 3.8. The $AlCl_3$ concen-

TABLE V

WEIGHT LOSS OF ALUMINUM ALLOY IN 7075 IN SATURATED
SOLUTIONS OF VARIOUS ALUMINUM SALTS

Solution	Duration of Test (days)	pH	Loss in Weight Average (mg/cm ²)
Al(CH ₃ COO) ₃	7	4.67	0.54
	10	4.92	0.42
Al(C ₆ H ₅ COO) ₃	7	3.40	0.13
	10	3.13	0.26
AlPO ₄	7	3.11	0.075
	7	2.84	0.11
Al(CrO ₄) ₃	7	3.52	0.005
	7	3.12	0.005
AlF ₃	7	4.90	(0.25)
	7		(0.24)

TABLE VI

WEIGHT LOSS OF ALUMINUM ALLOY 1199 in 0.5N SOLUTION
OF AlCl_3 AT DIFFERENT pH's

pH	Duration of Test (days)	Loss in Weight, Average (mg/cm^2)
2.0	7	0.64
3.0	7	0.49
3.5	7	0.46
4.0	7	0.34
4.5	7	0.24

TABLE VII

WEIGHT LOSS OF ALUMINUM ALLOY 1199 IN SOLUTIONS OF
APPROXIMATELY EQUIVALENT ACTIVITY

Solution	Duration of Test (days)	Molarity	Loss in Weight, Average (mg/cm ²)
$\text{Al}_2(\text{SO}_4)_3$	7	0.69	0.20
AlCl_3	7	0.014	0.68
$\text{Al}(\text{NO}_3)_3$	7	0.020	0.85

tration at a pH of 3.2 conforms to 0.24 eq/l AlCl_3 . They concluded that a NaCl solution did not activate the Al surface but highly basic AlCl_3 at the same pH (3.79) did. Solutions of AlCl_3 in concentrations of 0.1 and 1.0 eq/l activated Al in times decreasing with increased concentration while NaCl solutions at the same pH did not. Thus the "autocatalytic" nature of the process is not due to the pH or the Cl^- but the ability of the AlCl_3 solution to react with the oxide. The activation can be followed by the potential going negative, e.g. to -0.65 to -0.69 v (vs. Ag-AgCl reference) and the negative potential is due to the Al- AlCl_3 couple.

The present results support the concept that it is the nature of the aluminum salt rather than the pH of the solution produced by the hydrolysis of the aluminum cation. Thus, consistently aluminum sulfate solutions are non-corrosive and aluminum nitrate solutions accelerate corrosion. The results of these experiments emphasize the chemical nature of the process as opposed to strictly physical or electrochemical approaches. The results are inconsistent with some of the mechanisms proposed in the past particularly these that give to the chloride ion unique properties of adsorption and penetration of the oxide film.⁷

This approach is also inconsistent with those models that put a heavy emphasis on flaws and dislocations in the film.⁸ Presumably, all of the samples of a given alloy would have the same surface structure.

These experiments definitely demonstrate that aluminum salts in the 3.0-4.0 pH range are accelerators for aluminum corrosion. This effect is not restricted to aluminum chloride solutions. Whether or not they are the accelerators for aluminum pitting and aluminum stress cracking for these processes occurring in neutral salt solutions remains to be demonstrated.

REFERENCES

1. I.L. Rosenfeld and I.K. Marshakov, Corrosion 20, 115t-124t (1964).
2. B.F. Brown, C.T. Fujii and E.P. Dahlberg, J. Electrochem. Soc., 116, 218 (1969).
3. M. Marek, J.G. Rinker and R.F. Hochman, "Solution Chemistry in Crevices and Stress Corrosion Cracks," Presented at Sixth International Congress on Metallic Corrosion, Sydney, Australia, December 3-9, 1975.
4. J.A. Davis in "Localized Corrosion," pp. 168-172, ed. by R.W. Staehle, B.F. Brown, J. Kruger and A. Agrawal, National Association of Corrosion Engineers, Houston, Texas (1974).
5. T. Hagyard and J.R. Santhiapillai, J. Appl. Chem., 9, 323-330 (1959).
6. C. Edeleanu and U.R. Evans, Trans. Faraday Soc., 47, 1121 (1951).
7. H. Kaesche in "Localized Corrosion," ed. by R.W. Staehle, B.F. Brown, J. Kruger and A. Agrawal, pg. 516, National Association of Corrosion Engineers, Houston, Texas (1974).
8. M.J. Pryor, Z. für Elektrochemie, 62, 782 (1958).
9. J.A. Richardson and G.C. Wood, Corrosion Sci., 10, 313 (1970).

DISTRIBUTION LIST

Organization

Defense Documentation Center
Cameron Station
Alexandria, VA 22314

Office of Naval Research
Department of the Navy
800 N. Quincy Street
Arlington, VA 22217

ATTN: Code 471
Code 102
Code 470

Commanding Officer
Office of Naval Research
Branch Office
Building 114, Section D
666 Summer Street
Boston, MA 02210

Commanding Officer
Office of Naval Research
Branch Office
536 South Clark Street
Chicago, IL 60605

Office of Naval Research
San Francisco Area Office
One Hallidie Plaza Suite 601
San Francisco, CA 94102

Naval Research Laboratory
Washington, DC 20375

ATTN: Codes 6000
6100
6300
6400
2627

Naval Air Development Center
Code 382
Warminster, PA 18964
ATTN: Mr. F. S. Williams

Organization

Naval Air Propulsion Test Center
Trenton, NJ 08628
ATTN: Library

Naval Construction Battalion
Civil Engineering Laboratory
Port Hueneme, CA 93043
ATTN: Materials Division

Naval Electronics Laboratory
San Diego, CA 92152
ATTN: Electron Materials
Sciences Division

Naval Missile Center
Materials Consultant
Code 3312-1
Point Mugu, CA 92041

Commanding Officer
Naval Surface Weapons Center
White Oak Laboratory
Silver Spring, MD 20910
ATTN: Library

David W. Taylor Naval Ship
Research and Development Center
Materials Department
Annapolis, MD 21402

Naval Undersea Center
San Diego, CA 92132
ATTN: Library

Naval Underwater System Center
Newport, RI 02840
ATTN: Library

Naval Weapons Center
China Lake, CA 93555
ATTN: Library

Naval Postgraduate School
Monterey, CA 93940
ATTN: Mechanical Engineering
Department

Organization

Naval Air Systems Command
Washington, DC 20360
ATTN: Codes 52031
52032

Naval Sea System Command
Washington, DC 20362
ATTN: Code 035

Naval Facilities Engineering
Command
Alexandria, VA 22331
ATTN: Code 03

Scientific Advisor
Commandant of the Marine Corps
Washington, DC 20380
ATTN: Code AX

Naval Ship Engineering Center
Department of the Navy
Washington, DC 20360
ATTN: Code 6101

Army Research Office
P.O. Box 12211
Triangle Park, NC 27709
ATTN: Metallurgy & Ceramics Program

Army Materials and Mechanics
Research Center
Watertown, MA 02172
ATTN: Research Programs Office

Air Force Office of Scientific
Research
Bldg. 410
Bolling Air Force Base
Washington, DC 20332
ATTN: Chemical Science Directorate
Electronics & Solid State
Sciences Directorate

Air Force Materials Laboratory
Wright-Patterson AFB
Dayton, OH 45433

Library
Building 50, Rm 134
Lawrence Radiation Laboratory
Berkeley, CA

Organization

NASA Headquarters
Washington, DC 20546
ATTN: Code RRM

NASA
Lewis Research Center
21000 Brookpark Road
Cleveland, OH 44135
ATTN: Library

National Bureau of Standards
Washington, DC 20234
ATTN: Metallurgy Division
Inorganic Materials Div.

Director Applied Physics Laboratory
University of Washington
1013 Northeast Fortieth Street
Seattle, WA 98105

Defense Metals and Ceramics
Information Center
Battelle Memorial Institute
505 King Avenue
Columbus, OH 43201

Metals and Ceramics Division
Oak Ridge National Laboratory
P.O. Box X
Oak Ridge, TN 37380

Los Alamos Scientific Laboratory
P.O. Box 1663
Los Alamos, NM 87544
ATTN: Report Librarian

Argonne National Laboratory
Metallurgy Division
P.O. Box 229
Lemont, IL 60439

Brookhaven National Laboratory
Technical Information Division
Upton, Long Island
New York 11973
ATTN: Research Library

Office of Naval Research
Branch Office
1030 East Green Street
Pasadena, CA 91106

Dr. T. R. Beck
Electrochemical Technology Corporation
10035 31st Avenue, NE
Seattle, Washington 98125

Professor I. M. Bernstein
Carnegie-Mellon University
Schenley Park
Pittsburgh, Pennsylvania 15213

Professor H. K. Birnbaum
University of Illinois
Department of Metallurgy
Urbana, Illinois 61801

Dr. Otto Buck
Rockwell International
1049 Camino Dos Rios
P. O. Box 1085
Thousand Oaks, California 91360

Dr. David L. Davidson
Southwest Research Institute
8500 Culebra Road
P. O. Drawer 28510
San Antonio, Texas 78234

Dr. D. J. Duquette
Department of Metallurgical Engineering
Rensselaer Polytechnic Institute
Troy, New York 12181

Professor R. T. Foley
The American University
Department of Chemistry
Washington, D. C. 20016

Mr. G. A. Gehring
Ocean City Research Corporation
Tennessee Avenue & Beach Thorofare
Ocean City, New Jersey 08226

Dr. J. A. S. Green
Martin Marietta Corporation
1450 South Rolling Road
Baltimore, Maryland 21227

Professor R. H. Heidersbach
University of Rhode Island
Department of Ocean Engineering
Kingston, Rhode Island 02881

Professor H. Herman
State University of New York
Material Sciences Division
Stony Brook, New York 11970

Professor J. P. Hirth
Ohio State University
Metallurgical Engineering
1314 Kinnear Road
Columbus, Ohio 43212

Dr. E. W. Johnson
Westinghouse Electric Corporation
Research and Development Center
1310 Beulah Road
Pittsburgh, Pennsylvania 15235

Professor R. M. Latanision
Massachusetts Institute of Technology
77 Massachusetts Avenue
Room E19-702
Cambridge, Massachusetts 02139

Dr. F. Mansfeld
Rockwell International Science Center
1049 Camino Dos Rios
P. O. Box 1085
Thousand Oaks, California 91360

Dr. Jeff Perkins
Naval Postgraduate School
Monterey, California 93940

Professor H. W. Pickering
Pennsylvania State University
Department of Material Sciences
University Park, Pennsylvania 16802

Dr. E. A. Starke, Jr.
Georgia Institute of Technology
School of Chemical Engineering
Atlanta, Georgia 30332

Dr. Barry C. Syrett
Stanford Research Institute
333 Ravenswood Avenue
Menlo Park, California 94025

Dr. R. P. Wei
Lehigh University
Institute for Fracture and
Solid Mechanics
Bethlehem, Pennsylvania 18015

Professor H. G. F. Wilsdorf
University of Virginia
Department of Materials Science
Charlottesville, Virginia 22903

Dr. Clive Clayton
State University of New York
Material Sciences Division
Stony Brook, New York 11970