

AD-A081 250

NORTHWESTERN UNIV EVANSTON IL DEPT OF MATERIALS SCIENCE F/G 11/9
PIEZOELECTRICITY IN POLYACRYLONITRILE.(U)

JAN 80 H UEDA, S H CARR

N00014-75-C-0963


UNCLASSIFIED

TR-8

NL

[OF]

AD-A081 250

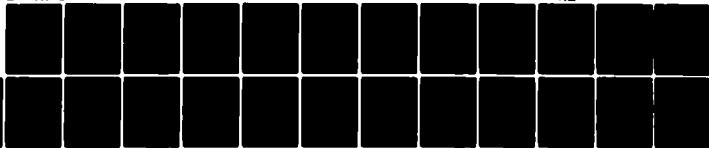

END
DATE
FILMED
3-80
DDC

AD A 081 250

DDC FILE COPY

OFFICE OF NAVAL RESEARCH
Contract No. N00014-75-C-0963

Project No. NR 051-599

TECHNICAL REPORT NO. 8
"PIEZOELECTRICITY IN POLYACRYLONITRILE"

by

H. Ueda and S. H. Carr

Prepared for Publication
in the
Journal of Macromolecular Science, Physics Edition

Materials Research Center
and
Department of Materials Science and Engineering
Northwestern University
Evanston, Illinois 60201

January 4, 1980

DTIC
ELECTE
FEB 27 1980
S D
A

Reproduction in whole or in part is permitted for
any purpose of the United States Government
Approved for Public Release; Distribution Unlimited

80 2 26 015

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 8	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) <u>PIEZOELECTRICITY IN POLYACRYLONITRILE</u>	5. TYPE OF REPORT & PERIOD COVERED (9) Interim Repts	
7. AUTHOR(s) 10) H. Ueda S. H. Carr	6. PERFORMING ORG. REPORT NUMBER 8	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Materials Research Center and Department of Materials Science and Engineering Northwestern University, Evanston, IL 60201	8. CONTRACT OR GRANT NUMBER(s) 15) N00014-75-C-0963 NSF-DMR 76-80847	
11. CONTROLLING OFFICE NAME AND ADDRESS ONR Branch Office 536 S. Clark Street Chicago, IL 60605	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS Project No. NR-051-599	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) (14) TR-8	12. REPORT DATE 11) 4 Jan 80 January 4, 1980	
	13. NUMBER OF PAGES 30	
	15. SECURITY CLASS. (of this report) Unclassified	
16. DISTRIBUTION STATEMENT (of this Report) See appended distribution list. 12) 30		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Polyacrylonitrile, electrical polarization, piezoelectric coefficients, ion-doping, space-charge.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The piezoelectricity and related properties in ion-doped ($\text{NH}_4^+\text{NO}_3^-$, NaNO_3^-) and undoped films of polyacrylonitrile have been measured as a function of temperature. The piezoelectric constants of both ion-doped and undoped films show a maximum around 80°C and thereafter decrease markedly with temperature. A maximum of thermally stimulated discharge current (TSDC) around 90°C is observed in both ion-doped and undoped films. An abrupt decrease of piezoelectric constant around 90°C and TSDC maximum around 90°C are ascribed to randomization of nitrile dipoles in ordered regions. The piezoelectric		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

260870

constant of stretched films has a tendency to increase with stretching. The piezoelectric constant, d_{31} , changes from positive to negative when temperature rises above 110°C .

sub 31

"PIEZOELECTRICITY IN POLYACRYLONITRILE"

Abstract

The piezoelectric and related properties in ion-doped (NH_4NO_3 , NaNO_3) and undoped films of polyacrylonitrile have been measured as a function of temperature. The piezoelectric constants of both ion-doped and undoped films show a maximum around 80°C and thereafter decrease markedly with temperature. A maximum of thermally stimulated discharge current (TSDC) around 90°C is observed in both ion-doped and undoped films. An abrupt decrease of piezoelectric constant around 90°C and TSDC maximum around 90°C are ascribed to randomization of nitrile dipoles in ordered regions. The piezoelectric constant of stretched films has a tendency to increase with stretching. The piezoelectric constant, d_{31} , changes from positive to negative when temperature rises above 110°C .

✓

17

INTRODUCTION

Piezoelectric properties have been investigated for a variety of polymers (1,2). Since the discovery of strong piezoelectric activity in stretched and poled polyvinylidene fluoride (PVDF) (3), PVDF has attracted special interest and has received a variety of practical applications. But a complete understanding of the piezoelectricity in polymers has not been achieved.

Space charges and/or preferred orientation of small parts of macromolecules having nonzero dipole moments are usually considered to be the origin of the residual polarization of electret polymers. If residual polarization arises from dipole orientation, a polymer which has large dipole moment may have high piezoelectric activity. The value of dipole moment per monomer unit of the form-I crystal of PVDF, which has high piezoelectric activity, is 2.1 Debye units. However, polyacrylonitrile (PAN) repeat units have dipole moments in excess of 3 Debye units, and its dipoles can be oriented by an applied electrical field (4,5). Thus, high piezoelectric activity of PAN is expected.

According to results of infrared internal reflection spectroscopic measurements by Stupp, et al., (5), randomization of oriented dipoles is thermally induced as the temperature is raised above 90°C. Around this temperature, both dielectric relaxation (11-14) and mechanical relaxation (8-10) have been observed. Therefore, one would expect the piezoelectric constant to decay irrecoverably in this temperature region.

Piezoelectricity arises from a combination of dielectric and elastic characteristics. Even though it is a rather complicated phenomenon, some information about chemical and/or physical structure of a polymer might be obtained from piezoelectric measurements, since piezoelectricity is strongly influenced by internal structure of the sample.

Many papers concerning the structure (16-21) and properties of PAN have been published, but the piezoelectricity of PAN has not been reported in any detail. In this paper, the results of the temperature dependence of the piezoelectric constant of PAN is reported.

EXPERIMENTAL

Polyacrylonitrile (PAN) was purified as follows: PAN powders were dissolved in dimethyl formamide (DMF) at a concentration of 5 wt%. The solution was then poured into distilled water to obtain purified PAN in a loose fibrous form. This PAN was again dissolved in DMF (2 wt%). PAN films were cast on a glass surface from the 2 wt% DMF solution under reduced pressure for 24 hours at room temperature. The cast films were then dried in an evacuated vacuum oven for 24 hours at 40°C. As-cast films were uniaxially stretched at 90°C and then annealed at 130°C for 30 min. Gold was evaporated onto each side of the sample to serve as electrodes. PAN films doped with NaNO_3 and NH_4NO_3 were prepared by first dissolving the salt in DMF and subsequently adding it dropwise to the PAN solution in DMF. The PAN powders were supplied from Standard Oil Company (Ohio), Cleveland, Ohio. The material is reported to have a weight average molecular weight in excess of 35,000. Thicknesses of samples ranged from 30 to 54 μm . Dimensions of film samples for piezoelectric measurements were 2 cm by 0.4 cm, and the area of electrode was 0.21 cm^2 . Dimensions of film samples for thermally stimulated discharge (TSD) measurements were 2.5 cm by 2.5 cm, and the area of electrode was 3.14 cm^2 .

A Rheovibron model DD-II (Toyo Kogyo Co., Japan) was used to measure the piezoelectric-strain constant, d_{31} , piezoelectric-stress constant, e_{31} , and elastic modulus, C . The 1-axis is taken along length (stretching direction) and 3-axis along thickness (poling direction). The dynamic stress and the piezoelectric polarization induced by applying a sinusoidal alternating strain of 11 Hz (with oscillating displacement strain of approximately 5×10^{-6}) were measured, and absolute values of d_{31} , e_{31} , and C were obtained. The piezoelectric polarization was detected using charge amplifier under short-circuit conditions. The measurement was made in the temperature region between room temperature and about 150°C, with a heating rate of about 1°C/min.

TSDC thermograms and direct current (d.c.) conductivity were recorded with an Electret Thermal Analyzer (Toyo-Seiki, Seisaku-Sho, Ltd.) (4). The heating rate was $2^{\circ}\text{C}/\text{min}$. All specimens that were polarized were held for 30 min. under the imposed electrical field at 130°C and then cooled at room temperature under the applied electrical field. The conditions of the specimens are listed in Table 1.

RESULTS

Figures 1 and 2 show the temperature-dependence of the piezoelectric-strain constant, d_{31} , and -stress constant, e_{31} , for stretched (2 times), designated PE, and unstretched, designated PN, PAN films. When tension is given to the specimen at room temperature, negative charge is induced on that surface to which the positive field was applied. In the case of stretched films, the piezo-exciting tension is applied in the direction of the orientation of molecular chains. In the temperature region below about 70°C, both d_{31} and e_{31} increase with temperature. However, above 80°C, d_{31} and e_{31} decrease remarkably. The piezoelectric constants of PE1 (first run of a plain, stretched specimen) show a second peak around 120°C. The piezoelectric constants for a second run, (PE2) at room temperature, are about 2.5×10^{-2} of those of the first run. The d_{31} - and e_{31} -constants of PN (a plain but not-stretched specimen) do not show the second peak, and these values at room temperature are about 0.2 of those of PE1.

Figure 3 shows the temperature-dependence of the dynamic elastic modulus, C , of unstretched film. The decrease of C around 50°C and the remarkable decrease above 70°C may be due to β -relaxation and α_a -relaxations, respectively, as observed by Okajima, *et al.* (7). Ishida, *et al.* (11) also confirmed the β -relaxation around 60°C (160Hz) in dielectric measurement, and they attributed it to a local mode relaxation.

Figure 4 represents the temperature-dependence of both of NH_4NO_3 - and NaNO_3 -doped films. The e_{31} -constants decrease steeply above 80°C, in the same manner as those of undoped films. The d_{31} -constants for each of these samples are listed in Table 1. Since material AE (doped with ammonium nitrate and stretched) and SN (doped with sodium nitrate but not stretched) had been polarized under a field of 2×10^4 V/cm and 1×10^4 V/cm respectively, the

observed d_{31} -constants of AE and those of SN are multiplied by normalizing factor 2.5 and 5, respectively. It is observed that the piezoelectric constants of PAN have a tendency to increase with elongation. Polarization by high intensity electrical field also induces high piezoelectric activity.

DISCUSSION

The piezoelectric constants of unpolarized film is negligible, and the piezoelectric constants of the second run of a polarized film are very small as compared to those of its first run, as shown in Figures 1 and 2. This indicates that the piezoelectricity of PAN arises from the residual polarization induced by applying an electric field to the specimen.

Such polarization arises in PAN from a partial preferred orientation of dipoles and from space charge effects. Ion-doped PANs are expected to exhibit greatly magnified space charge effects, as the ions deliberately added have mobilities suitable for their being displaced during poling treatments. Since space charges tend to be trapped at a boundary between two different phases, electrical polarization due to space charge should be stabilized in inhomogeneous system. This effect is expected to be important in the case of PAN, because it is inferred to have "structure" at the 10's of Angstroms size scale. Miyachi and Andrews (10) suggested a three-phase structure consisting of two different amorphous phases (one more ordered or strongly cohesively bonded than the other) and a crystalline phase. Hinrichsen and Orth (18) proposed a two-phase structure based on an observation of electron micrograph of the surface of drawn PAN. Recent work by Stupp and Carr (22) contributes further to clarifying this issue. It is thought that polarization due to space charge may be stable in PAN based on its homogeneity and its large nitrile dipole moment.

Figure 5 represents TSD thermograms of both ion-doped and undoped films. One notes the existence of a depolarization current peak around 90°C in both ion-doped and undoped film. The maximum is not observed in the second run (P2). As expected, the depolarization current is increased by ion-doping. This result supports the notion that the apparent residual polarization is increased by ions. The total charge, Q , released around 90°C for A (containing

ammonium nitrate) and P1 (plain) is about 2×10^{-6} Coul./cm² and 1.8×10^{-7} Coul./cm², respectively. One sees, therefore, that Q for NH_4NO_3 -doped films is about ten times that of undoped PAN. It is obvious that the large apparent residual polarization of ion-doped film is due to the ions serving as space charges; the value of nitrile side group dipole moment should not be influenced by the presence of ions. One would ordinarily expect that ion-doped films might have high piezoelectric activity if the piezoelectricity arises from the residual polarization due to space charge. As shown in Table 1, the piezoelectric constants of ion-doped film at room temperature fail to reflect the enhanced persistent polarization that the dopant ions create.

In the temperature region where the TSDC shows maximum, loss of the preferred nitrile dipole orientation along the thickness direction has been confirmed from ATR analysis by Stupp and Carr (5). Piezoelectric constants also decrease remarkably in the same temperature region. Such a decrease in piezoelectric constants associated with an increase of D.C. conductivity has been observed for some polymers (23,24). If the decrease of both d_{31} and e_{31} (shown in Figures 1 and 2) is principally caused by the electrical conductivity, both d_{31} and e_{31} of ion-doped films should decrease at lower temperatures than those of undoped films, because of their relatively high electrical conductivity of ion-doped films, as shown in Figure 6. Figure 6 shows the second run of the temperature dependence of D.C. conductivity. According to Figure 4, the e_{31} -constants of ion-doped films decrease steeply in the same temperature region as that of undoped films. Depolarization current maximum around 90°C is also observed in both the doped film and the undoped film. The result suggests that the abrupt decrease in the piezoelectric constant of PAN around 90°C can be attributed to randomization of nitrile dipoles. It follows that the main origin of piezoelectricity below

100°C can probably be ascribed to the orientation of nitrile dipoles.

Piezoelectric constant is increased by stretching, as shown in Table 1. This can be explained as follows: the preferential orientation of the main chains induces an increase of the orientation of nitrile side groups into planes tending to be perpendicular to the stretching direction. This evidence is consistent with other experimental results. Comstock, et al. (4) noted that stretching PAN to its natural draw ratio (4x) permits a substantial increase in polarization from TSD measurements. The increase of the infrared dichroic ratio of nitrile stretching band (2700 cm^{-1}) due to drawing was also confirmed by Bohn, et al. (16). Similarly, it is well known that stretched and poled PVDF has very high piezoelectric activity (3,25).

The piezoelectric constant of PAN is smaller than that of PVDF in spite of the large dipole moment of nitrile groups. Such low piezoelectric activity of PAN may result from the following. The residual polarization due to dipoles is small and the degree of rotation of nitrile dipoles due to applied strain is also small. Since these factors are strongly dependent upon the microstructure and crystallinity (order) of the specimen, the difference in piezoelectric activity between PAN and PVDF is probably caused by the difference in the inter- and intra-chain molecular organization between them. Chains in Form-I PVDF, the crystal polymorph having high piezoelectric activity, have a planar zig-zag conformation, and most of CF_2 dipoles orient in a common direction perpendicular to the chain backbones (26,27).

Bohn, et al. (16) proposed a single phase-laterally ordered model. They believed that the nitrile groups protrude through the cylinder wall of chain in random locations, owing to irregular kinking of the chain. Lindenmeyer (15) suggested, based on the average distance along the c-direction per monomer unit, that the chains are coiled in some sort of helical conformation. Calvin and Storr (20) also suggested a helical configuration for PAN. Hinrich-

sen, et al. (18) proposed a two-phase structure consisting of more and less ordered regions with planar zig-zag conformation in ordered regions. Recently, Warner, et al. (21) presented a rod-like model consisting of ordered and less ordered regions and a contorted helical conformation with the nitrile group oriented at various angles to the axis of the rod within each rod.

Although many details of structure of PAN are not clarified, it may be thought that the regularity in structure in PAN is less than that of PVDF. The arrangement of nitrile groups in ordered regions seems to be a crucial aspect of electrical polarization and piezoelectricity of PAN. The evidence of relative low piezoelectric activity suggests the random orientation of nitrile dipoles in ordered regions. This suggestion is consistent with the result obtained by Bohn, et al. (16) that the dichroic ratios are not very high, even at very high degrees of chain orientation in the fibers.

It is reasonable to think that the piezoelectricity arises principally from the residual polarization in ordered regions rather than that in unordered regions. According to the above supposition, the remarkable decrease in both d_{31} and e_{31} around 90°C is due to the randomization of nitrile dipoles in ordered regions. The molecular motion around 90°C and at high temperature region have been observed in various measurements. Nevertheless, the molecular characterizations of these relaxations or transitions are not clear. Minami, et al. (9) ascribed the mechanical relaxations around 110°C (110 cps) and 160°C to a molecular motion in paracrystalline regions and amorphous regions, respectively. Imai, et al. (8) demonstrated that completely amorphous PAN does not show mechanical relaxation around 95°C (110 Hz) and solution grown crystals give a high intensity of relaxation about 95°C but no relaxation around 140°C . Bohn, et al. (16) and Hinrichsen (18) observed a transitional change of interchain distance around 90°C .

Two mechanisms for piezoelectricity due to orientating dipoles are 1)

intrinsic piezoelectricity due to the rotation of dipoles, and 2) apparent piezoelectricity due to the combination of electrostriction constant and the residual polarization (2). According to the phenomenological theory of piezoelectricity of inhomogeneous system (28,29), the increase of both d_{31} and e_{31} in the temperature region below 80°C may be due to one or more of the following factors: 1) the increase of dielectric constant in amorphous phases, (2) the decrease of elastic modulus in piezoelectric phases, and (3) the increase of electrostriction constant in amorphous phases. Although it is known that the temperature-dependence of piezoelectricity in electret polymers is affected by the change of electrostriction constant with temperature (2), it remains unknown at present which factor is the main reason for the increase of piezoelectric constants below 80°C in PAN. A similar ambiguity likewise applies to our current understanding of piezoelectricity in PVDF (29).

The sign of piezoelectric constant of PAN changes above 110°C . When the specimen is stretched above 110°C , positive charge (negative charge below 110°C) is induced on the surface of specimen to which a positive electrical field is supplied. Some authors have observed the sign reversal of piezoelectric constant due to the reasons: 1) the sign reversal of the piezoelectric constant in piezoelectric phases (30) or (2) a phase angle exceeding 90 degrees of complex piezoelectric constant which arises from Maxwell-Wagner effect (31). The sign reversal of the electrostriction coefficient, and the coexistence of two origins of piezoelectricity (which are opposite in sign), are considered as other reasons for sign reversal of piezoelectric constant. The reason for the sign reversal of the piezoelectric constant of PAN is not clear at present. Somewhat complicated factors, one of them being thermal degradation, should be taken into account when the properties of PAN at high temperature are considered.

CONCLUSIONS

The piezoelectric constants of electrically polarized films of purified PAN decrease abruptly with temperature around 90°C. The decrease of piezoelectric constant around 90°C is ascribed to the randomization of nitrile dipoles in ordered regions. The piezoelectric constants of ion-doped films (NH_4NO_3 , NaNO_3) also decrease with temperature around 90°C. In the same temperature range, a sharp decrease of elastic modulus and a maximum of depolarization current of both undoped and ion-doped films are observed. Even though the total charge released around 90°C of NH_4NO_3 -doped film (2×10^{-4} mole/gm PAN) is about ten times that of undoped films, the piezoelectric constants of ion-doped films are almost the same, or even less than, those of undoped films at room temperature. The sign of piezoelectric constant, d_{31} , changes from positive to negative above 110°C.

ACKNOWLEDGEMENTS

The authors wish to express their appreciation of financial support provided generously by the Chemistry Program of the Office of Naval Research. Some use was made of research facilities provided by the Northwestern University Materials Research Center, which is funded by the Materials Research Laboratory Program of the National Science Foundation (grant DMR 76-80847).

REFERENCES

1. E. Fukada, Adv. Biophys., 6, 121 (1974).
2. R. Hayakawa and Y. Wada, Adv. Polym. Sci., 11, 1 (1973).
3. M. Kawai, Jpn. J. Appl. Phys., 8, 975 (1969).
4. R. J. Comstock, S. I. Stupp and S. H. Carr, J. Macromol. Sci., Phys., B13(1), 101 (1977).
5. S. I. Stupp and S. H. Carr, J. Polym. Sci., Polym. Phys. Ed., 16, 13 (1978).
6. G. R. Cotten and W. C. Schneider, Kolloid Z. Z. Polym., 192, 16 (1963).
7. S. Okajima, M. Ikeda and A. Takeuchi, J. Polym. Sci., A-1, 6, 1925 (1968).
8. Y. Imai, S. Minami, T. Yoshihara, Y. Joh and H. Sato, Polymer Letters, 8, 281 (1970).
9. S. Minami, T. Yoshihara and H. Sato, Kobunshi Kagaku, 1, 125 (1972).
10. K. Miyachi and R. D. Andrews, Appl. Polym. Sym. No. 25, 127 (1974).
11. Y. Ishida, O. Amano and M. Takayanagi, Kolloid Z., 172, 129 (1960).
12. Y. Ishida, M. Matsuo, Y. Ueno and M. Takayanagi, Kolloid-Z. Z. Polym., 199, 67 (1964).
13. L. K. H. Van Beek, J. Appl. Polym. Sci., 9, 553 (1965).
14. R. Hayakawa, T. Nishi, K. Arisawa and Y. Wada, J. Polym. Sci., A-2, 5, 165 (1967).
15. P. H. Lindenmeyer, J. Appl. Phys., 34, 42 (1963).
16. C. R. Bohn, J. R. Schaefgen and W. O. Statton, J. Polym. Sci., 55, 531 (1961).
17. J. Koenig, J. Macromol. Sci., Phys., B4(3), 491 (1970).
18. G. Hinrichsen and H. Orth, Polym. Letters, 9, 529 (1971).
19. G. Hinrichsen, J. Polym. Sci., C No. 38, 303 (1972).
20. B. G. Calvin and P. Storr, Europ. Polym. J., 10, 337 (1974).
21. S. B. Warner, L. H. Peebles, Jr., D. R. Uhlmann, Office of Naval Research Technical Report No. 1, for Contract N00014-75-C-0542 (1978).

22. S. I. Stupp and S. H. Carr, Colloid and Polymer Science 257, 913 (1979).
23. T. Furukawa and E. Fukada, Jap. J. Appl. Phys., 16, 453 (1977).
24. E. Fukada, H. Ueda and R. Rinaldi, Biophys. J., 16, 911 (1976).
25. N. Murayama, J. Polym. Sci., Phys., 13, 929 (1975); 14, 989 (1976).
26. R. Hasegawa, Y. Takahashi, Y. Chatani and H. Tadokoro, Polym. J., 3, 600 (1972).
27. J. B. Lando, H. G. Olf and A. Peterlin, J. Polym. Sci., A-1, 4, 941 (1966).
28. M. Date, Polymer J., 8, 60 (1975).
29. T. Furukawa, J. Aiba and E. Fukada, J. Appl. Phys., 50(5), 3615 (1979).
30. S. Sasaki and E. Fukada, J. Poly. Sci., 14, 565 (1976).
31. H. Ueda and E. Fukada, Polym. J., 11, 103 (1979).

Table 1

Code	Dopant Species	Dopant Concentration*	Poling Field (V/cm)	Elongation Ratio	$10^8 \times d_{31}$ (cgsesu)		
					room temp.	around 85°C	around 120°C
PE	none	--	5×10^4	2	1.7	4.3	3.6
PN	none	--	5×10^4	1	0.32	0.65	--
AE	NH_4NO_3	2×10^{-4}	2×10^4	2	0.26(0.65)**	0.80(2.0)**	1(2.5)**
SN	NaNO_3	2×10^{-4}	1×10^4	1	0.07(0.35)**	0.16(0.8)**	8(40)**
PE(10^5)	none	--	10×10^4	2	3.0	6.3	10.7

*Molar concentration units: moles salt per gram PAN. For example, 1×10^{-4} mol/gram PAN = $0.85 \text{ wt\% salt} = 5.3 \times 10^{-3}$ mol/AN residue.

**Normalized to be equivalent to a poling field of 5×10^4 V/cm.

FIGURE CAPTIONS

- Figure 1. Temperature-dependence of d_{31} -constants for stretched (PE) and unstretched (PN) polyacrylonitrile poled at 130°C under 5×10^4 V/cm for 30 min. PE 1 = the first run; PE 2 = the second run (cooled after the first run without an applied field).
- Figure 2. Temperature-dependence of the e_{31} -constants for stretched and unstretched polyacrylonitrile poled at 130°C under 5×10^4 V/cm for 30 min. PE 1 = the first run; PE 2 = the second run (cooled after the first run without an applied field).
- Figure 3. Temperature-dependence of the elastic modulus, C , for unstretched polyacrylonitrile measured at 11 Hz.
- Figure 4. Temperature-dependence of the e_{31} -constants for NH_4NO_3 -doped and stretched (AE) and NaNO_3 -doped but unstretched (SN) polyacrylonitrile. Specimens were poled at 130°C under 2×10^4 V/cm and 1×10^4 V/cm respectively for 30 min.
- Figure 5. Thermally stimulated depolarization currents from undoped (P) and from ion-doped polyacrylonitrile (A = NH_4NO_3 doped film; S = NaNO_3 doped film) poled at 130°C for 30 min. P1 = the first measurement, P2 = the second measurement (cooled after the first run without an applied field). Heating rate was $2^{\circ}\text{C}/\text{min}$.

Figure 6. Temperature-dependence of the second run of d.c. conductivity (cooled after the first measurement under an applied field) for NaNO_3 doped and undoped polyacrylonitrile measured at heating rate of $2^\circ\text{C}/\text{min}$. P = undoped film; S1 = 2×10^{-5} [mole/gm PAN] NaNO_3 doped film; and S2 = 5×10^{-4} [mole/gm PAN] NaNO_3 doped film. Doped specimens were poled under an electrical field of 5×10^3 V/cm, and undoped films were poled using 1×10^4 V/cm.





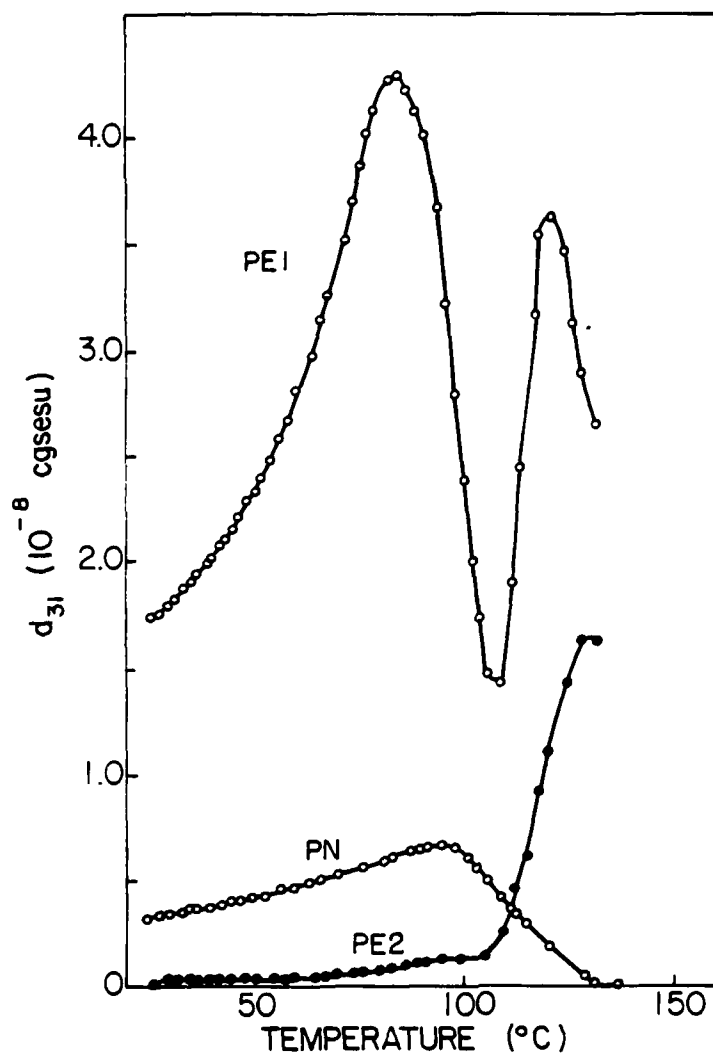



Fig. 1

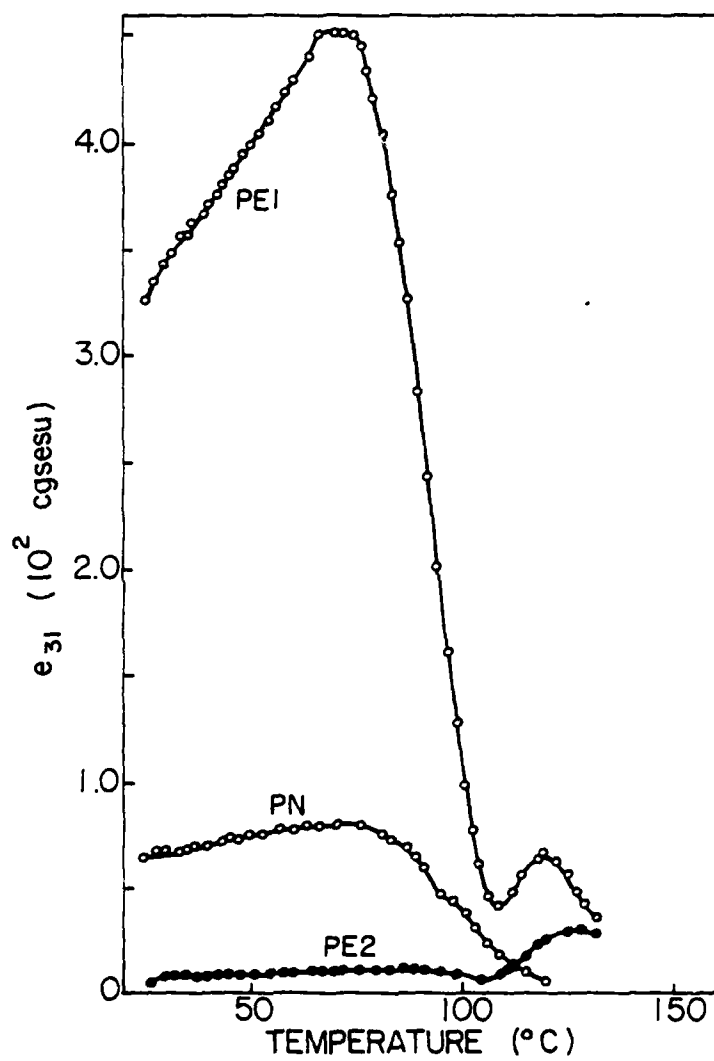

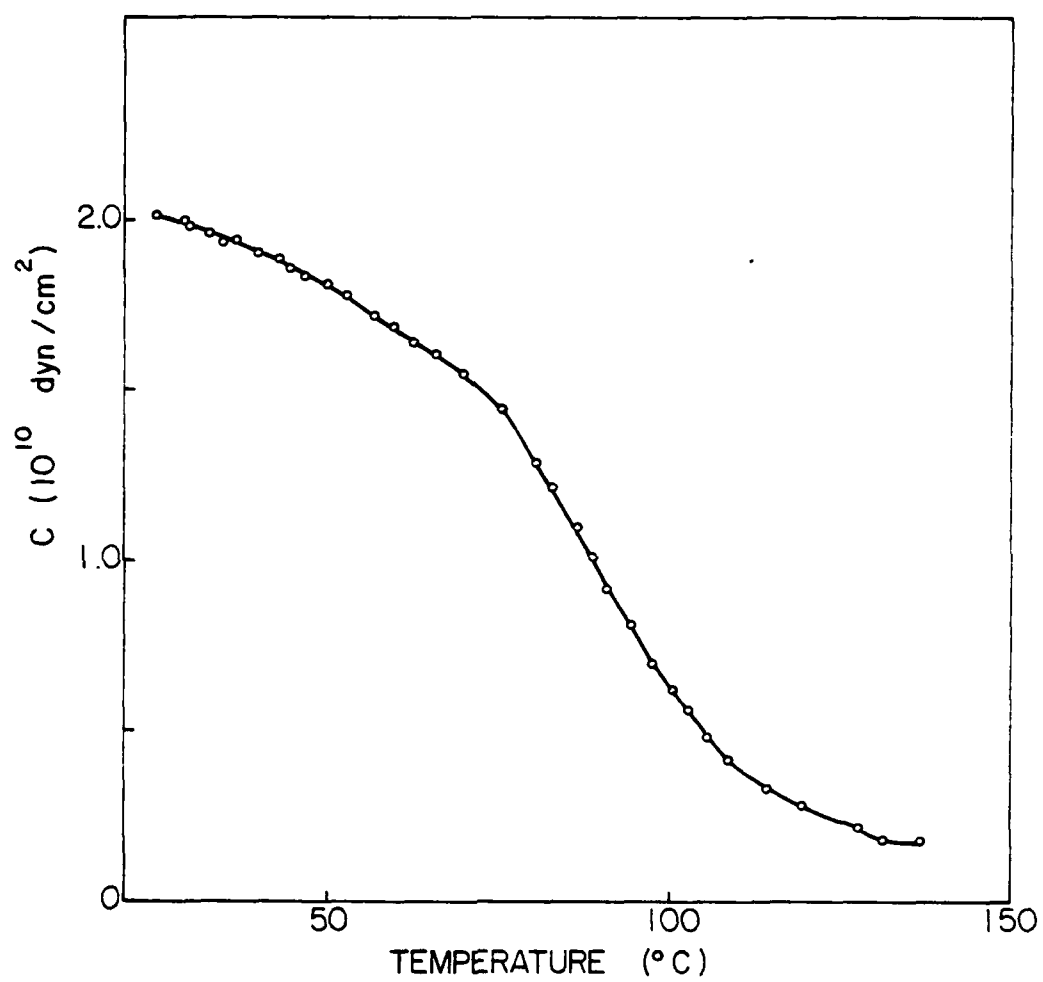

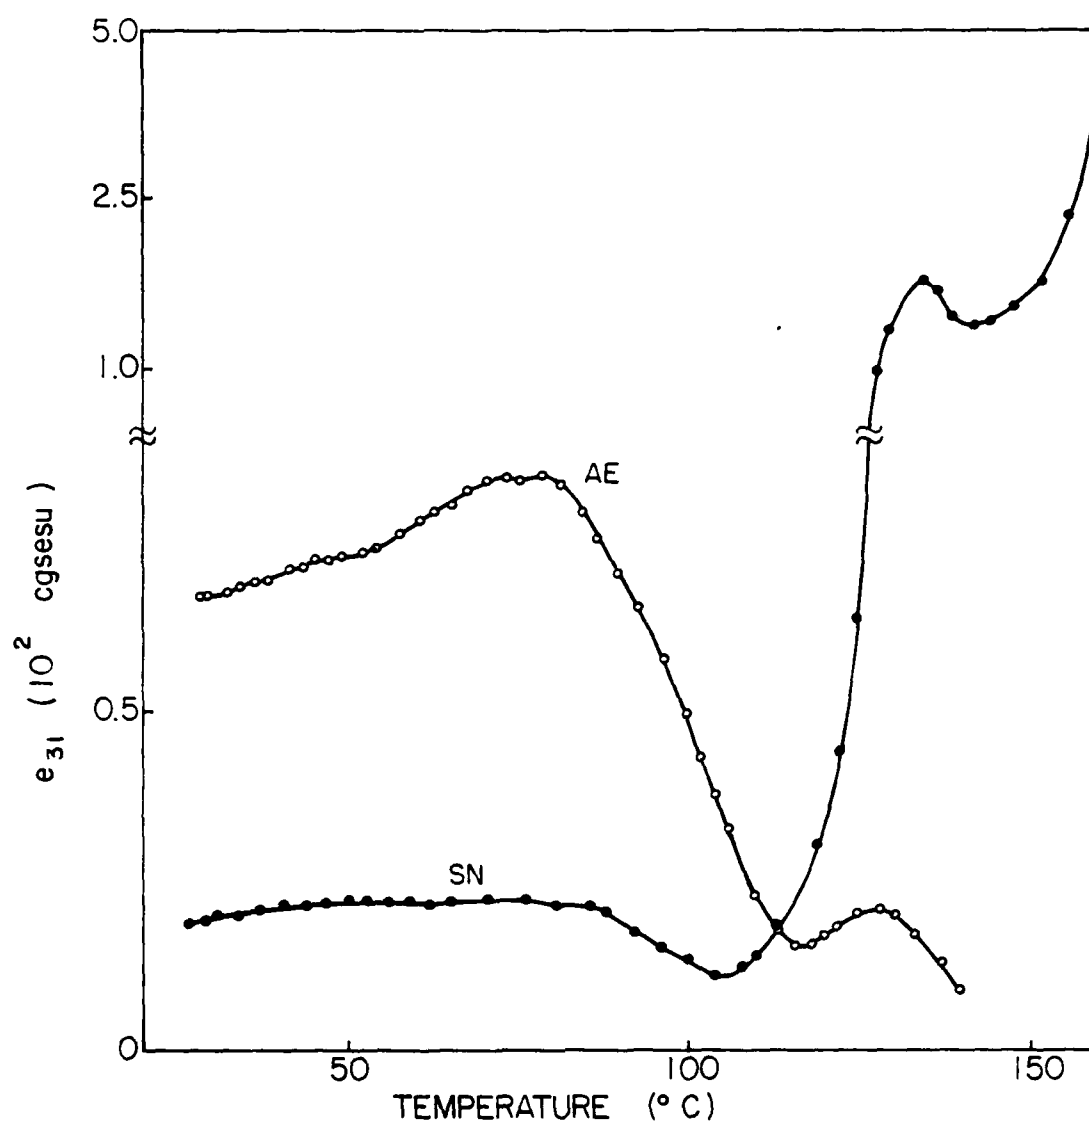

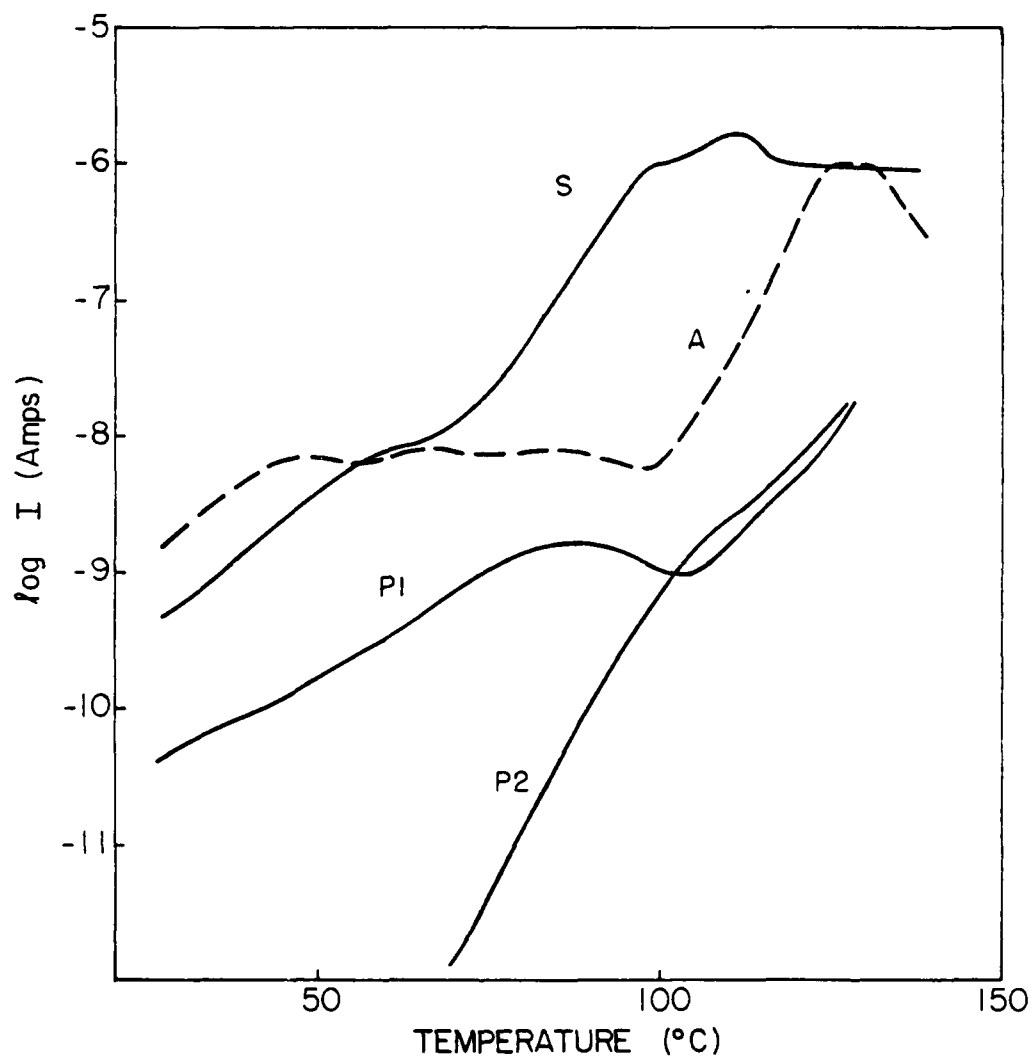

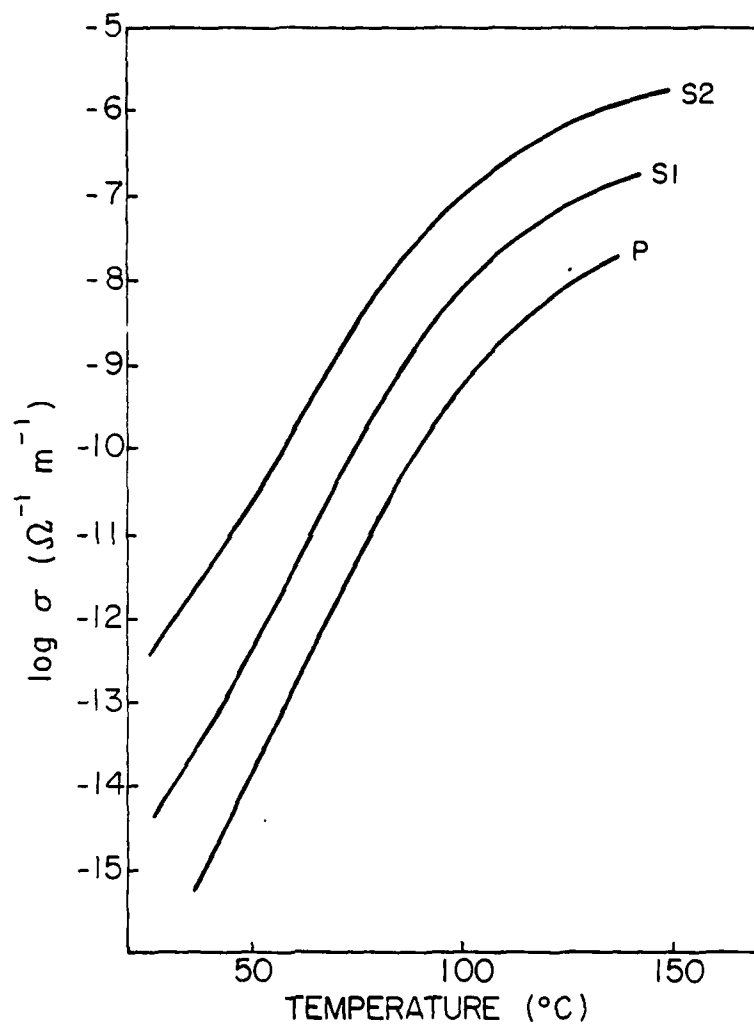

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research 800 North Quincy Street Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. George Sandoz	1	U.S. Army Research Office P.O. Box 1211 Research Triangle Park, N.C. 27709 Attn: CRD-AA-IP	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Mr. Joe McCartney	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Weapons Center China Lake, California 93555 Attn: Dr. A. B. Amster Chemistry Division	1
ONR Area Office One Hallidie Plaza, Suite 601 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Naval Civil Engineering Laboratory Port Hueneme, California 93401 Attn: Dr. R. W. Drisko	1
ONR Branch Office Building 114, Section D 666 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Professor K. E. Woehler Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Washington, D.C. 20390 Attn: Code 6100	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (R,E&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research 800 N. Quincy Street Arlington, Virginia 22217 Attn: Dr. Richard S. Miller	1
Commander, Naval Air Systems Command Department of the Navy Washington, D.C. 20360 Attn: Code 310C (H. Rosenwasser)	1	Naval Ship Research and Development Center Annapolis, Maryland 21401 Attn: Dr. G. Bosmajian Applied Chemistry Division	1
		Naval Ocean Systems Center San Diego, California 91232 Attn: Dr. S. Yamamoto, Marine Sciences Division	1

Encl 1

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Mr. Robert W. Jones Advanced Projects Manager Hughes Aircraft Company Mail Station D 132 Culver City, California 90230	1	Dr. T. J. Reinhart, Jr., Chief Composite and Fibrous Materials Branch Nonmetallic Materials Division Department of the Air Force Air Force Materials Laboratory (AFSC) Wright-Patterson Air Force Base, Ohio	1 454
Dr. C. Giori IIT Research Institute 10 West 35 Street Chicago, Illinois 60616	1	Dr. J. Lando Department of Macromolecular Science Case Western Reserve University Cleveland, Ohio 44106	
Dr. M. Litt Department of Macromolecular Science Case Western Reserve University Cleveland, Ohio 44106	1	Dr. J. White Chemical and Metallurgical Engineering University of Tennessee Knoxville, Tennessee 37916	1
Dr. R. S. Roe Department of Materials Science and Metallurgical Engineering University of Cincinnati Cincinnati, Ohio 45221	1	Dr. J. A. Manson Materials Research Center Lehigh University Bethlehem, Pennsylvania 18015	1
Dr. L. E. Smith U.S. Department of Commerce National Bureau of Standards Stability and Standards Washington, D.C. 20234	1	Dr. R. F. Helmreich Contract RD&E Dow Chemical Co. Midland, Michigan 48640	1
Dr. Robert E. Cohen Chemical Engineering Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1	Dr. R. S. Porter University of Massachusetts Department of Polymer Science and Engineering Amherst, Massachusetts 01002	1
Dr. David Roylance Department of Materials Science and Engineering Massachusetts Institute of Technology Cambridge, Massachusetts 02039	1	Professor Garth Wilkes Department of Chemical Engineering Virginia Polytechnic Institute and State University Blacksburg, Virginia 24061	1
Dr. T. P. Conlon, Jr., Code 3622 Sandia Laboratories Sandia Corporation Albuquerque, New Mexico 87115	1	Dr. Kurt Baum Fluorochem Inc. 6233 North Irwindale Avenue Azusa, California 91702	
Dr. Martin Kaufmann, Head Materials Research Branch, Code 4542 Naval Weapons Center China Lake, California 93555	1	Professor C. S. Paik Sung Department of Materials Sciences and Engineering Massachusetts Institute of Technology Cambridge, Massachusetts 02139	

TECHNICAL REPORT DISTRIBUTION LIST, 356A

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. L. A. Smith Singer Aerospace Kearfelt Division 1150 McBride Avenue Little Falls, NJ 07424	1	Picatinny Arsenal SMUPA-FR-M-D Dover, New Jersey 07801 Attn: A. M. Anzalone Building 3401	1
Dr. M. Broadhurst Bulk Properties Section National Bureau of Standards U.S. Department of Commerce Washington, D.C. 20234	2	Dr. J. K. Gillham Princeton University Department of Chemistry Princeton, New Jersey 08540	1
Dr. T. A. Litovitz Department of Physics Catholic University of America Washington, D.C. 20017	1	Douglas Aircraft Co. 3855 Lakewood Boulevard Long Beach, California 90846 Attn: Technical Library CI 290/36-84 AUTO-Sutton	1
Dr. E. V. Subramanian Washington State University Department of Materials Science Pullman, Washington 99163	1	Dr. E. Baer Department of Macromolecular Science Case Western Reserve University Cleveland, Ohio 44106	1
Dr. M. Shen Department of Chemical Engineering University of California Berkeley, California 94720	1	Dr. K. D. Pae Department of Mechanics and Materials Science Rutgers University New Brunswick, New Jersey 08903	1
Dr. V. Stannett Department of Chemical Engineering North Carolina State University Raleigh, North Carolina 27607	1	NASA-Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135 Attn: Dr. T. T. Serofini, MS-49-1	1
Dr. D. R. Uhlmann Department of Metallurgy and Material Science Center for Materials Science and Engineering Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1	Dr. Charles H. Sherman, Code TD 121 Naval Underwater Systems Center New London, Connecticut 06340	1
Naval Surface Weapons Center White Oak Silver Spring, Maryland 20910 Attn: Dr. J. M. Augl Dr. B. Hartman	1	Dr. William Risen Department of Chemistry Brown University Providence, Rhode Island 02192	1
Dr. G. Goodman Globe Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1	Dr. Alan Gent Department of Physics University of Akron Akron, Ohio 44304	1