

AD-A092 197

OKLAHOMA UNIV NORMAN SCHOOL OF AEROSPACE MECHANICAL --ETC F/G 11/4
VIBRATION OF CYLINDRICAL SHELLS OF BIMODULUS COMPOSITE MATERIAL--ETC(U
OCT 80 C W BERT, M KUMAR

N00014-78-C-0647

UNCLASSIFIED

OU-AMNE-80-20

NL

1-1

2002


END

DATE

FILED

1 8/9

DTIC

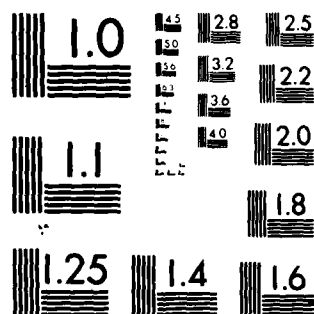

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A092197

LEVEL ¹¹

(12)

Department of the Navy
OFFICE OF NAVAL RESEARCH
Structural Mechanics Program
Arlington, Virginia 22217

¹⁵
Contract N00014-78-C-0647

Project NR 064-609

⁹ Technical Report No. 19

¹⁴ Report OU-AMNE-80-20, TR-191

⁶ VIBRATION OF CYLINDRICAL SHELLS
OF BIMODULUS COMPOSITE MATERIALS.

by

¹⁰ Cw. Bert ~~and~~ M. Kumar

DEC 1 1980

¹¹ Oct 1980

¹² 32

School of Aerospace, Mechanical and Nuclear Engineering
University of Oklahoma
Norman, Oklahoma 73019

Approved for public release; distribution unlimited

DDC FILE COPY

400497
80 11 25 002

VIBRATION OF CYLINDRICAL SHELLS OF
BIMODULUS COMPOSITE MATERIALS

Charles W. Bert^{*} and M. Kumar[†]
University of Oklahoma, Norman, Oklahoma

Abstract

A theory is formulated for the small-amplitude free vibration of thick, circular cylindrical shells laminated of bimodulus composite materials, which have different elastic properties depending upon whether the fiber-direction strain is tensile or compressive. The theory used is the dynamic, shear deformable (moderately thick shell) analog of the Sanders best first-approximation thin-shell theory. By means of tracers, the analysis can be reduced to various simpler shell theories, namely Love's first approximation, and Donnell's shallow-shell theory. As an example of the application of the theory, a closed-form solution is presented for a freely supported panel or complete shell. To validate the analysis, numerical results are compared with existing results for various special cases. Also, the effects of the various shell theories, thickness shear flexibility, and bimodulus action are investigated.

Index categories: Structural Dynamics; Structural Composite Materials.

^{*}Benjamin H. Perkinson Professor of Engineering, School of Aerospace, Mechanical and Nuclear Engineering. Associate Fellow, AIAA.

[†]Graduate Research Assistant, School of Aerospace, Mechanical and Nuclear Engineering.

Nomenclature

- A_{ij} = stretching stiffnesses
 B_{ij} = bending-stretching coupling stiffnesses
 b = circumferential arc width of panel
 $[C]$ = matrix of coefficients
 C_ℓ, C'_ℓ = shell-theory tracers
 $\bar{C}_\ell$ = C_ℓ/R
 D_{ij} = bending stiffnesses
 d_{xy} = $\partial^2(\quad)/\partial x \partial y$
 h = total shell thickness
 I = rotatory inertia coefficient (per unit midsurface area)
 K_4, K_5 = thickness-shear correction factors
 $[L]$ = matrix of linear differential operators
 M_i, N_i = stress couples and in-surface stress resultants
 m, n = axial and circumferential mode numbers
 P = normal inertia coefficient (per unit midsurface area)
 Q_i = thickness-shear stress resultants
 Q_{ijkl} = plane-stress reduced stiffness coefficients
 R = radius of shell midsurface
 S_{ij} = thickness-shear stiffnesses
 t = time
 u, v, w = axial, circumferential, and radial midsurface displacements
 U, V, W = amplitudes of u, v, w
 x, y, z = position coordinates in axial, circumferential, and outward normal directions
 X, Y = amplitudes of ψ_1 and ψ_2

z_{nx}, z_{ny} = neutral-surface positions for $\epsilon_x=0$ and $\epsilon_y=0$, respectively

Z_x, Z_y = $z_{nx}/h, z_{ny}/h$

α, β = $m\pi/L, n\pi/b$ (for panel) or n/R (for complete cylinder)

δ, Δ = generalized displacement vectors defined in Eqs. (8) and (15)

ψ_1, ψ_2 = bending slopes in xz and yz planes

ϵ_j = strain components at arbitrary location (x, y, z)

ϵ_j^0 = midsurface strain components

κ_j = curvature-change components

ρ = material density

σ_i = stress components

ω = natural frequency

$()_{,xy} = \partial^2()/\partial x \partial y$

Accession For	
NTIS GRA&I	✓
DTIC TAB	
Unannounced	
Justification	
By	
Distribution	
Availability Codes	
Dist	
A	

Introduction

Analysis of composite-material shell-type structures has been of considerable research interest in the past two decades. Earlier work has been summarized in a monograph by Leissa¹ and in two more recent survey papers^{2,3}.

Due to its importance, the finite-length circular cylindrical shell configuration has received the most attention. Thin-shell analyses of composite-material shells of this configuration have been performed by Dong⁴, Abhat and Wilcox⁵ and Fortier and Rossettos⁶ using Donnell's shallow-shell theory⁷, by Bert, Baker, and Egle⁸, Stavsky and Loewy⁹, Shivakumar and Krishna Murty¹⁰, and Greenberg and Stavsky¹¹ using Love's first approximation theory¹², and by Padovan¹³ using Novozhilov's higher-order theory¹⁴. In the present work, tracer coefficients are introduced to consider Sanders' best first-approximation theory¹⁵, Love's first approximation¹², Loo's¹⁶, Morley's¹⁷, and Donnell's⁷ theories.

The thickness shear moduli of composite materials are typically an order of magnitude lower than their in-plane elastic moduli. This is in contrast to isotropic materials, which have shear to elastic moduli ratios of approximately 40%. Thus, composite-material shells would be expected to be affected by thickness-shear flexibility to a much greater extent than isotropic shells having the same geometric parameters. Previous research on vibration of laminated, shear deformable shells includes that of Refs. 18 and 19, using the shear deformable analog of Donnell's shallow shell theory, and Refs. 20 and 21, using the shear deformable version of Love's first approximation. In some recent work²², the shear deformable analog of Sanders' theory was developed and it was shown, using tracers, that this theory can be reduced to two simpler shear deformable theories as special cases: (1) Love's first approximation and Loo's, and (2) Morley's and Donnell's. This approach is extended to shell vibration in the present paper.

Certain fiber-reinforced materials, especially those with very soft matrices (e.g., cord-rubber), exhibit quite different elastic behavior depending upon whether the fiber-direction strain is tensile or compressive²³⁻²⁵. As a first approximation, the stress-strain behavior of such materials is usually modeled as being bilinear, with different elastic coefficients depending upon the sign of the fiber-direction strain. Thus, these materials are called bimodulus composite materials. The fiber-governed, symmetric-compliance material model proposed in Ref. 26 has been shown to agree well with experimental data obtained under in-plane loading of several materials with drastically different properties in tension and compression. To the best of the present investigators' knowledge, all of the previous investigations of laminated bimodulus shells, as reviewed in Refs. 22 and 27, have involved

the static behavior of thin cylindrical shells under mechanical or thermal loading. However, free vibration of cross-ply laminated plates was considered in Ref. 28.

Formulation

Laminate Action

To explain the effect of bimodulus action on the shell behavior, we discuss first a flat plate. If a single-layer plate or a laminate symmetrically laminated about its midplane are made of ordinary (not bimodulus) materials, there is no coupling between bending and stretching. However, a laminate which is not symmetrically laminated does exhibit bending-stretching coupling.

Now consider a flat plate consisting of either a single layer of bimodulus material or symmetrically laminated of bimodulus materials. When the plate is subjected to bending, the different elastic moduli in tension and compression cause a shift in the neutral surface away from the geometric midplane toward the tension side of the bend if the tensile properties exceed the compressive ones. Consequently, this plate displays bending-stretching coupling, analogous to a plate unsymmetrically laminated of ordinary material as described in the preceeding paragraph. Therefore, in a laminated bimodulus-material shell, bending-stretching coupling can be induced by the combination of bimodulus-material action, laminate configuration, and shell geometry (curvature).

One can write the laminate constitutive relations as

$$\begin{aligned} \begin{Bmatrix} N_i \\ M_i \end{Bmatrix} &= \begin{bmatrix} A_{ij} & B_{ij} \\ B_{ij} & D_{ij} \end{bmatrix} \begin{Bmatrix} \epsilon_j^0 \\ \kappa_j \end{Bmatrix} & (i,j=1,2,6) \\ \{Q_i\} &= [S_{ij}] \{\epsilon_j\} & (i,j=4,5) \end{aligned} \quad (1)$$

Here, the respective in-plane, bending-stretching, bending or twisting, and thickness-shear stiffnesses are defined as

$$(A_{ij}, B_{ij}, D_{ij}) = \int_{-h/2}^{h/2} (1, z, z^2) Q_{ijk\ell} dz \quad (i, j=1, 2, 6) \quad (2)$$

$$S_{ij} = \int_{-h/2}^{h/2} K_i K_j Q_{ijk\ell} dz \quad (i, j=4, 5)$$

Here, $Q_{ijk\ell}$ denotes the plane-stress reduced stiffness defined by

$$\{\sigma_i\} = [Q_{ijk\ell}] \{\epsilon_j\} \quad (3)$$

and subscripts ij refer to the position in the stress-strain-relation array, k refers to the sign of the fiber-direction strain ($1 \sim +$, $2 \sim -$), and ℓ is the layer number.

Shear Deformable Shell Theory

The coordinate system used here is shown in Fig. 1. Then the equations of motion in the absence of body forces and body moments can be written as

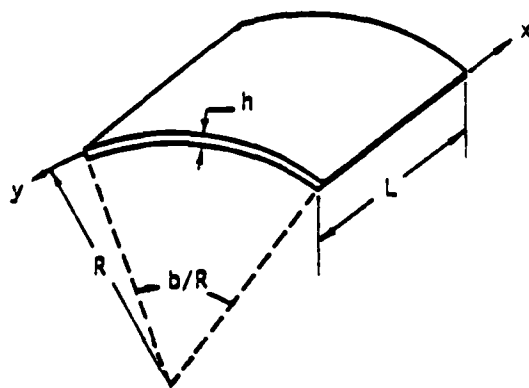


Figure 1. Shell geometry

$$\begin{aligned}
N_{1,x} + N_{6,y} - (C_2/2R)M_{6,y} &= Pu_{,tt} + (I/R)\psi_{1,tt} \\
N_{6,x} + N_{2,y} + (C_1/R)Q_4 + (C_2/2R)M_{6,x} &= Pv_{,tt} + (I/R)\psi_{2,tt} \\
Q_{5,x} + Q_{4,y} - (N_2/R) &= Pw_{,tt} \\
M_{1,x} + M_{6,y} - Q_5 &= I\psi_{1,tt} + (I/R)u_{,tt} \\
M_{6,x} + M_{2,y} - Q_4 &= I\psi_{2,tt} + (I/R)v_{,tt}
\end{aligned} \tag{4}$$

Here, it has been assumed that the mass distribution is symmetric about the middle surface. The normal and rotatory inertias are

$$(P, I) = \int_{-h/2}^{h/2} (1, z^2) \rho \, dz \tag{5}$$

The first terms on the right side of each of Eqs. (4) are the same as for plates in Mindlin's shear deformable theory²⁹. The second terms on the right side of all except the third equation of set (4) are the inertia-coupling terms due to shell curvature, first introduced by Mirsky and Herrmann³⁰.

The kinematics of deformation can be expressed as

$$\begin{aligned}
\epsilon_1^0 &= u_{,x} \quad ; \quad \epsilon_2^0 = v_{,y} + (w/R) \quad ; \quad \epsilon_6^0 = u_{,y} + v_{,x} \\
\epsilon_4 &= \psi_2 + w_{,y} - (C_1/R)v \quad ; \quad \epsilon_5 = \psi_1 + w_{,x} \\
\kappa_1 &= \psi_{1,x} \quad ; \quad \kappa_2 = \psi_{2,y} \quad ; \quad \kappa_6 = \psi_{1,y} + \psi_{2,x} + (C_2/2R)(v_{,x} - u_{,y})
\end{aligned} \tag{6}$$

The coefficients C_ℓ appearing in Eqs. (4) and (6) are shell-theory tracers which take on values listed in Table 1. Note that in contrast to the case of thin-shell theory, Loo's approximation offers no simplification over Love's first-approximation theory and Donnell's theory coincides with Morley's.

Table 1. Shell-theory tracers and their values

Theory (thin-shell theory generalized to shear deformable theory)	C_1	C_2
Sanders ¹⁵	1	1
Love's first approximation ¹² and Loo's ¹⁶	1	0
Morley's ¹⁷ and Donnell's ⁷	0	0

Substituting Eqs. (1) and (6) into Eqs. (4), one obtains the following operator equation

$$[L]\{\delta\} = 0 \quad (7)$$

where

$$\{\delta\} = \{u, v, w, \psi_1, \psi_2\}^T \quad (8)$$

and $[L]$ is a symmetric matrix of linear differential operators listed in Appendix A.

Criteria for Homogeneity Along the Middle Surface

In deriving Eq. (7), we tacitly assumed that the laminate stiffnesses ($A_{ij}, B_{ij}, D_{ij}, S_{ij}$) are all independent of coordinates (x, y) on the middle surface. However, in view of the bimodulus nature of the materials comprising the laminate, these stiffnesses depend upon the fiber-direction neutral-surface positions associated with the respective layers (i.e., z_{nx} for a single layer with axially oriented fibers, and z_{nx} and z_{ny} for a cross-ply laminate).

Thus, for layers having the fibers oriented axially, the associated fiber-direction neutral-surface position is determined by

$$\epsilon_1 = \epsilon_1^0 + z_{nx}\kappa_1 = 0$$

or

$$z_{nx} = -\epsilon_1^0/\kappa_1 = -u_{,x}/\psi_{1,x} = \text{constant} \quad (9)$$

Similarly, for layers having the fibers oriented circumferentially

$$\epsilon_2 = \epsilon_2^0 + z_{ny} \kappa_2 = 0$$

or

$$z_{ny} = -\epsilon_2^0 / \kappa_2 = -(v_{,y} + R^{-1}w) / \psi_{2,y} = \text{constant} \quad (10)$$

Closed-Form Solution

We seek a solution which satisfies the governing operator Eq. (7), the homogeneity relations (9) and (10), and appropriate boundary conditions.

A closed-form solution is presented for a shell that is freely supported (simply supported without in-surface restraint; SS3 in Hoff's notation³¹) along its curved edges:

$$\begin{aligned} N_1(0,y,t) &= N_1(L,y,t) = M_1(0,y,t) = M_1(L,y,t) = 0 \\ w(0,y,t) &= w(L,y,t) = v(0,y,t) = v(L,y,t) = 0 \\ \psi_2(0,y,t) &= \psi_2(L,y,t) = 0 \end{aligned} \quad (11)$$

The shell may be either circumferentially complete (closed), which requires that the circumferential mode shapes be periodic in position (i.e., trigonometric functions), or a cylindrically curved panel (open shell) freely supported along the generators, which requires that the following additional boundary conditions be satisfied:

$$\begin{aligned} N_2(x,0,t) &= N_2(x,b,t) = M_2(x,0,t) = M_2(x,b,t) = 0 \\ w(x,0,t) &= w(x,b,t) = u(x,0,t) = u(x,b,t) = 0 \\ \psi_1(x,0,t) &= \psi_1(x,b,t) = 0 \end{aligned} \quad (12)$$

Under these conditions, the solution to Eq. (7) is of the form

$$\begin{aligned}
u &= U \cos \alpha x \sin \beta y \cos \omega t \\
v &= V \sin \alpha x \cos \beta y \cos \omega t \\
w &= W \sin \alpha x \sin \beta y \cos \omega t \\
\psi_1 &= X \cos \alpha x \sin \beta y \cos \omega t \\
\psi_2 &= Y \sin \alpha x \cos \beta y \cos \omega t
\end{aligned}
\tag{13}$$

where $\alpha = m\pi/L$ and $\beta = n\pi/b$ for a panel and n/R for a complete cylinder.

Substitution of Eqs. (13) into Eq. (7) leads to the following homogeneous algebraic system

$$[C]\{\Delta\} = \{0\} \tag{14}$$

where $[C]$ is a matrix with elements depending upon A_{ij} , B_{ij} , D_{ij} , S_{ij} , P , I , α , and β , and

$$\{\Delta\} = \{U, V, W, X, Y\}^T \tag{15}$$

Numerical Results

Before proceeding to the calculations for shells laminated of bimodulus materials, we present some results for both circumferentially complete cylinders and cylindrically curved panels laminated of ordinary composite materials.

The first example is for a thin-walled complete cylinder cross-plyed of boron-epoxy. The geometric parameters and material properties used are listed in Table 2. The agreement between the natural frequencies for numerous modes computed by use of the thin-shell theory of Appendix B (specialized to Love's first approximation) and the Love's first-approximation analysis of Ref. 8 is excellent, as shown by comparison of columns 3 and 4 in Table 3. The inclusion of thickness shear deformation sometimes

decreases the natural frequencies, but in other instances increases them, as can be seen in column 5 of Table 3. For this thin shell, the effect of rotatory inertia is almost negligible (column 6).

The second example is for a cylindrically curved panel with thickness shear flexibility included, using numerical input data from Refs. 18 and 19 as listed in Table 4. In order to make a fair comparison with the results of Refs. 18 and 19, it is necessary to use the shear deformable version of Donnell's theory and to neglect rotatory inertia and the tangential inertias ($P_{u,tt}$ and $P_{v,tt}$) as suggested by Vlasov³². Dimensionless natural frequencies for various modes, with and without bending-stretching coupling (B_{ij}) suppressed, are listed in Tables 5 and 6. The lack of good agreement in Table 5 is difficult to explain, especially in view of the good agreement in Table 6.

In studying the above results, one can discern these general trends:

1. For a complete shell at a fixed axial wave number, the natural frequencies first decrease then increase with increasing circumferential wave number (n). As was first explained by Arnold and Warburton³³, this is due to the decrease in membrane strain energy and the increase in bending strain energy as n is increased.
2. The inclusion of thickness shear deformation and rotatory inertia does not always decrease the frequency. A similar observation may be seen in the recent work of Greenberg and Stavsky³⁴.
3. Bending-stretching coupling ($B_{ij} \neq 0$) always lowers the natural frequency compared to the value for the uncoupled case ($B_{ij} = 0$).
4. If the frequencies are normalized with the panel width (b), as in Table 6, increasing the aspect ratio (L/b) lowers the frequency values, just as it does in the case of a flat panel (plate).

To illustrate the effects of bimodulus composite-material action, aramid-rubber properties, determined primarily from the experiments of Patel et al.²⁴ by use of the material model of Ref. 26, are used. Some details of the estimation of certain properties not directly measured in Ref. 24 are given in Ref. 28. The complete set of properties used is listed in Table 7. This material has the most drastic difference between tensile and compressive properties known to the present investigators; thus, it is definitely a worst case.

Although the present problem is a linear one in each portion of a cycle of vibration, it actually is different in the two portions of a cycle. This phenomenon was explained for the vibration of single-layer and two-layer, cross-ply plates in Ref. 28. Here, for completeness, we discuss the cross-ply case: side cross-sectional views are shown in Fig. 2. The inner layer is oriented circumferentially (y direction) and the outer layer is oriented axially (x direction). During the first portion of a cycle, consider the shell to be deflected as shown in Fig. 2(a). Then the neutral surface for ϵ_x falls outside of the interface within the axially oriented layer, while the neutral surface for ϵ_y lies inside the interface, i.e., within the circumferential layer. In the latter portion of the vibration cycle, Fig. 2(b), the ϵ_x neutral surface falls outside the axial layer, and the ϵ_y neutral surface lies outside of the circumferential layer. Therefore, in the latter portion of the cycle, compressive properties are used for the entire axial layer and tensile properties for the entire circumferential layer. From the foregoing considerations for a two-layer, cross-ply shell, it is clear that the stiffnesses acting in the two portions of a cycle, (a) and (b) in Fig. 2, are different and thus the associated frequencies

(denoted by ω_1 and ω_2 , respectively) are also different. The corresponding time intervals over which the two portions take place are π/ω_1 and π/ω_2 . Thus, the total period for a complete cycle is $(\pi/\omega_1) + (\pi/\omega_2)$. The average frequency (ω) over the entire cycle is 2π divided by the total period; then

$$\omega^{-1} = (1/2)(\omega_1^{-1} + \omega_2^{-1}) \quad (16)$$

As discussed above, the neutral-surface positions are different during the two portions of a cycle; numerical results are listed in Table 8. The average frequency, as calculated from Eq. (16), is plotted in Fig. 3 versus aspect ratio for various values of R/h . The dashed line shows the analogous results from Ref. 28. for flat plates.

As was mentioned in Ref. 28, it can be shown that in the bilinear analysis presented, energy is conserved at the junction between the two portions of the vibrational cycle.

Concluding Remarks

Two analyses have been presented for prediction of the free-vibrational behavior of freely supported, cylindrically curved panels or complete cylindrical shells cross-ply laminated of bimodulus composite materials. One analysis is for thin shells and the other is for moderately thick shells with thickness shear deformation and rotatory inertia included. When reduced to the special case of ordinary material, the solutions yielded results which agreed well with various existing numerical results. The peculiarities of bimodulus shells have been discussed and the effects of a limited number of parameters investigated. These results may be used to validate numerical analyses, such as those based on the finite-element method.

Acknowledgments

The authors acknowledge the financial support of the Office of Naval Research through Contract N00014-78-C-0647 and the computing time provided by the University's Merrick Computing Center.

References

- ¹ Leissa, A.W., *Vibration of Shells*, NASA SP-288, 1973.
- ² Bert, C.W. and Francis, P.H., "Composite Material Mechanics: Structural Mechanics," *AIAA Journal*, Vol. 12, No. 9, Sept. 1974, pp. 1173-1186.
- ³ Bert, C.W., "Vibration of Composite Structures," *Proceedings, International Conference on Recent Advances in Structural Dynamics*, Institute of Sound and Vibration Research, University of Southampton, Southampton, England, July 7-11, 1980, Vol. 2, pp. 693-712.
- ⁴ Dong, S.B., "Free Vibrations of Laminated Orthotropic Cylindrical Shells," *Journal of the Acoustical Society of America*, Vol. 44, No. 6, Dec. 1968, pp. 1628-1635.
- ⁵ Abhat, O.B. and Wilcox, M.W., "Dynamic Response of Laminated Composite Circular Cylindrical Shells with Freely Supported or Clamped Edges," *Developments in Mechanics*, Vol. 7 (Proc., 13th Midwestern Mechanics Conference), University of Pittsburgh, Pittsburgh, PA, 1973, pp. 579-592.
- ⁶ Fortier, R.C. and Rossettos, J.N., "Effects of Inplane Constraints and Curvature on Composite Plate Behavior," *International Journal of Solids and Structures*, Vol. 10, No. 12, Dec. 1974, pp. 1417-1429.
- ⁷ Donnell, L.H., "Stability of Thin-Walled Tubes under Torsion," Rept. 479, 1933, NACA.
- ⁸ Bert, C.W., Baker, J.L., and Egle, D.M., "Free Vibrations of Multilayer Anisotropic Cylindrical Shells," *Journal of Composite Materials*, Vol. 3, No. 3, July 1969, pp. 480-499.
- ⁹ Stavsky, Y. and Loewy, R., "On Vibrations of Heterogeneous Orthotropic Cylindrical Shells," *Journal of Sound and Vibration*, Vol. 15, No. 2, Mar. 22, 1971, pp. 235-256.
- ¹⁰ Shivakumar, K.N. and Krishna Murty, A.V., "Vibrations of Multifiber Composite Shells — Some Numerical Results," *Journal of Structural Mechanics*, Vol. 4, No. 4, 1976, pp. 379-393.
- ¹¹ Greenberg, J.B. and Stavsky, Y., "Vibrations of Composite Aeolotropic Cylindrical Shells," *AIAA/ASME/ASCE/AHS 21st Structures, Structural Dynamics, and Materials Conference*, Seattle, WA, May 12-14, 1980, Part 2, pp. 822-831.
- ¹² Love, A.E.H., *A Treatise on the Mathematical Theory of Elasticity*, 4th ed., Cambridge University Press, London, 1927 (Dover, New York, NY, 1944), pp. 528-532.
- ¹³ Padovan, J., "Numerical Analysis of Asymmetric Frequency and Buckling Eigenvalues of Prestressed Rotating Anisotropic Shells of Revolution," *Computers and Structures*, Vol. 5, No. 2/3, June 1975, pp. 145-154.
- ¹⁴ Novozhilov, V.V., *The Theory of Thin Shells*, Noordhoff, Groningen, the Netherlands, 1959, Chap. 1.
- ¹⁵ Sanders, J.L., Jr., "An Improved First-Approximation Shell Theory," Report R-24, June 1959, NASA.
- ¹⁶ Loo, T.T., "An Extension of Donnell's Equation for a Circular Cylindrical Shell," *Journal of the Aeronautical Sciences*, Vol. 24, 1957, pp. 390-391.
- ¹⁷ Morley, L.S.D., "An Improvement on Donnell's Approximation for Thin-Walled Circular Cylinders," *Quarterly Journal of Mechanics and Applied Mathematics*, Vol. 12, 1959, pp. 89-99.

- ¹⁸ Fortier, R.C. and Rossettos, J.N., "On the Vibration of Shear Deformable Curved Anisotropic Plates," *Journal of Applied Mechanics*, Vol. 40, No. 1, Mar. 1973, pp. 299-301.
- ¹⁹ Sinha, P.K. and Rath, A.K., "Vibration and Buckling of Cross-Ply Laminated Circular Cylindrical Panels," *Aeronautical Quarterly*, Vol. 26, No. 3, Aug. 1975, pp. 211-218.
- ²⁰ Dong, S.B. and Tso, F.K.W., "On a Laminated Orthotropic Shell Theory Including Transverse Shear Deformation," *Journal of Applied Mechanics*, Vol. 39, No. 4, Dec. 1972, pp. 1091-1096.
- ²¹ Rath, B.K. and Das, Y.C., "Vibration of Layered Shells," *Journal of Sound and Vibration*, Vol. 28, No. 4, June 22, 1973, pp. 737-757.
- ²² Hsu, Y.S., Reddy, J.N., and Bert, C.W., "Thermoelasticity of Circular Cylindrical Shells Laminated of Bimodulus Composite Materials," Contract N00014-78-C-0647, Report OU-AMNE-80-14, July 1980, School of Aerospace, Mechanical and Nuclear Engineering, University of Oklahoma, Norman, OK.
- ²³ Clark, S.K., "The Plane Elastic Characteristics of Cord-Rubber Laminates," *Textile Research Journal*, Vol. 33, No. 4, Apr. 1963, pp. 295-313.
- ²⁴ Patel, H.P., Turner, J.L., and Walter, J.D., "Radial Tire Cord-Rubber Composites," *Rubber Chemistry and Technology*, Vol. 49, No. 4, Sept.-Oct. 1976, pp. 1095-1110.
- ²⁵ Bert, C.W., "Micromechanics of the Different Elastic Behavior of Filamentary Composites in Tension and Compression," *Mechanics of Bimodulus Materials*, AMD Vol. 33, ASME, NY, 1979, pp. 17-28.
- ²⁶ Bert, C.W., "Model for Fibrous Composites with Different Properties in Tension and Compression," *Journal of Engineering Materials and Technology*, Trans. ASME, Vol. 99H, No. 4, Oct. 1977, pp. 344-349.
- ²⁷ Bert, C.W. and Sudhakar Reddy, V., "Cylindrical Shells of Bimodulus Composite Material," Contract N00014-78-C-0647, Report OU-AMNE-80-3, Feb. 1980, School of Aerospace, Mechanical and Nuclear Engineering, University of Oklahoma, Norman, OK; presented at the ASCE Annual Convention and Exposition, Hollywood-by-the-Sea, FL, Oct. 26-31, 1980.
- ²⁸ Bert, C.W., Reddy, J.N., Chao, W.C., and Sudhakar Reddy, V., "Vibration of Thick Rectangular Plates of Bimodulus Composite Material," Contract N00014-78-C-0647, Report OU-AMNE-80-8, May 1980, School of Aerospace, Mechanical and Nuclear Engineering, University of Oklahoma, Norman, OK.
- ²⁹ Mindlin, R.D., "Influence of Rotatory Inertia and Shear on Flexural Motion of Isotropic Elastic Plates," *Journal of Applied Mechanics*, Vol. 18, No. 1, Mar. 1951, pp. 31-38.
- ³⁰ Mirksy, I. and Herrmann, G., "Nonaxially Symmetric Motions of Cylindrical Shells," *Journal of the Acoustical Society of America*, Vol. 29, No. 4, Oct. 1957, pp. 1116-1123.
- ³¹ Hoff, N.J., "Buckling of Axially Compressed Circular Cylindrical Shells at Stresses Smaller than the Classical Value," *Journal of Applied Mechanics*, Vol. 32, No. 3, Sept. 1965, pp. 542-546.
- ³² Vlasov, V.Z., *General Theory of Shells and Its Applications in Engineering*, GITTL, Moscow, 1949; English translation, TT F-99, NASA, Apr. 1964, pp. 535-536.
- ³³ Arnold, R.N. and Warburton, G.B., "Flexural Vibrations of the Walls of Thin Cylindrical Shells Having Freely Supported Ends," *Proceedings, Royal Society, London*, Ser. A, Vol. 197, 1949, pp. 238-256.
- ³⁴ Greenberg, J.B. and Stavsky, Y., "Vibrations of Axially Compressed Laminated Orthotropic Cylindrical Shells, Including Transverse Shear Deformation," *Acta Mechanica*, Vol. 37, 1980, pp. 13-28.

Appendix A: Linear Differential Operators Appearing in Eq. (7)

$$\begin{aligned}
 L_{11} &= A_{11}d_x^2 + (A_{66} - \bar{C}_2B_{66} + \frac{1}{4}\bar{C}_2^2D_{66})d_y^2 - Pd_t^2 \\
 L_{12} &= (A_{12} + A_{66} - \frac{1}{4}\bar{C}_2^2D_{66})d_xd_y \\
 L_{13} &= (A_{12}/R)d_x \quad ; \quad L_{14} = B_{11}d_x^2 + (B_{66} - \frac{1}{2}\bar{C}_2D_{66})d_y^2 - (I/R)d_t^2 \\
 L_{15} &= (B_{12} + B_{66} - \frac{1}{2}\bar{C}_2D_{66})d_xd_y \\
 L_{22} &= (A_{66} + \bar{C}_2B_{66} + \frac{1}{4}\bar{C}_2^2D_{66})d_x^2 + A_{22}d_y^2 - \bar{C}_1^2S_{44} - Pd_t^2 \\
 L_{23} &= (R^{-1}A_{22} + \bar{C}_1S_{44})d_y \quad ; \quad L_{24} = (B_{12} + B_{66} + \frac{1}{2}\bar{C}_2D_{66})d_xd_y \\
 L_{25} &= (B_{66} + \frac{1}{2}\bar{C}_2D_{66})d_x^2 + B_{22}d_y^2 + \bar{C}_1S_{44} - (I/R)d_t^2 \\
 L_{33} &= -S_{55}d_x^2 - S_{44}d_y^2 + (A_{22}/R^2) + Pd_t^2 \\
 L_{34} &= (R^{-1}B_{12} - S_{55})d_x \quad ; \quad L_{35} = (R^{-1}B_{22} - S_{44})d_y \\
 L_{44} &= D_{11}d_x^2 + D_{66}d_y^2 - S_{55} - Id_t^2 \quad ; \quad L_{45} = (D_{12} + D_{66})d_xd_y \\
 L_{55} &= D_{66}d_x^2 + D_{22}d_y^2 - S_{44} - Id_t^2 \quad ; \quad \bar{C}_2 = C_2/R \quad ; \quad d_x = \partial(\quad)/\partial x
 \end{aligned}$$

Appendix B: Thin-Shell Theory

The theory developed here is an extension of the static bimodulus-composite shell analysis presented in Ref. 27. The shell theory used is a generalized first-approximation one that can be reduced to the theories of Sanders, Love's first-approximation, Loo, Morley, and Donnell by use of the tracers listed in Table B-1. It is emphasized that these are different tracers than those listed in Table 1.

The shell constitutive equations are the same as given in Eqs. (1)-(3), except now the thickness shear quantities (Q_4 and Q_5) are not needed. The appropriate equations of motion are

$$\begin{aligned}
N_{1,x} + N_{6,y} - (C'_4/R)M_{6,y} &= Pu_{,tt} \\
N_{6,x} + N_{2,y} + (C'_3/R)M_{6,x} + (C'_1/R)M_{2,y} &= Pv_{,tt} \\
M_{1,xx} + 2M_{6,xy} + M_{2,yy} - (N_2/R) &= Pw_{,tt}
\end{aligned} \tag{B1}$$

The kinematic relations for the middle-surface strains are the same as in Eqs. (6). Since now the thickness shear strains (ϵ_4 and ϵ_5) are identically zero, the curvatures are given by

$$\begin{aligned}
\kappa_1 &= -w_{,xx} \quad ; \quad \kappa_2 = -w_{,yy} + (C'_2/R)v_{,y} \\
\kappa_6 &= -2w_{,xy} + (C'_3/R)v_{,x} - (C'_4/R)u_{,y}
\end{aligned} \tag{B2}$$

Substituting the expressions for the middle-surface strains and curvatures into the constitutive relations and the latter into Eqs. (B1), one obtains the same form of operator expression as Eq. (7) except that now the elements of the $\{\delta\}$ vector are only u, v, w . The linear differential operators are now

$$\begin{aligned}
L_{11} &= A_{11}d_x^2 + [A_{66} - 2C'_4B_{66}R^{-1} + (C'_4)^2D_{66}R^{-2}]d_y^2 - Pd_t^2 \\
L_{12} &= [A_{12} + A_{66} + C'_2B_{12}R^{-1} + (C'_3 - C'_4)B_{66}R^{-1} - C'_3C'_4D_{66}R^{-2}]d_x d_y \\
L_{13} &= -B_{11}d_x^3 - (B_{12} + 2B_{66} - 2C'_4D_{66}R^{-1})d_x d_y^2 + A_{12}R^{-1}d_x = L_{31} \\
L_{21} &= [A_{12} + A_{66} + C'_1B_{12}R^{-1} + (C'_3 - C'_4)B_{66}R^{-1} - C'_3C'_4D_{66}R^{-2}]d_x d_y \\
L_{22} &= [A_{66} + 2C'_3B_{66}R^{-1} + (C'_3)^2D_{66}R^{-2}]d_x^2 \\
&\quad + [A_{22} + (C'_1 + C'_2)B_{22}R^{-1} + C'_1C'_2D_{22}R^{-2}]d_y^2 - Pd_t^2 \\
L_{23} &= -[B_{12} + 2B_{66} + C'_1D_{12}R^{-1} + C'_3D_{66}R^{-1}]d_x^2 d_y \\
&\quad - (B_{22} + C'_1D_{22}R^{-1})d_y^3 + (A_{22} + C'_1B_{22}R^{-1})R^{-1}d_y
\end{aligned}$$

$$\begin{aligned}
L_{32} = & - [B_{12} + 2B_{66} + C_2^1 D_{12} R^{-1} + 2C_3^1 D_{66} R^{-1}] d_x^2 d_y \\
& - (B_{22} + C_2^1 D_{22} R^{-1}) d_y^3 + (A_{22} + C_2^1 B_{22} R^{-1}) R^{-1} d_y \\
L_{33} = & D_{11} d_x^4 + 2(D_{12} + 2D_{66}) d_x^2 d_y^2 + D_{22} d_y^4 \\
& - 2B_{12} R^{-1} d_x^2 - 2B_{22} R^{-1} d_y^2 + A_{22} R^{-2} + P d_t^2
\end{aligned} \tag{B3}$$

Note that the operators L_{rs} are symmetric for all of the theories except Morley's.

The criteria for the neutral-surface locations (z_{nx} and z_{ny}) to be constant are now

$$\begin{aligned}
z_{nx} &= u_{,x}/w_{,xx} = \text{const.} \\
z_{ny} &= (v_{,y} + R^{-1}w)/(w_{,yy} - C_2^1 R^{-1}v_{,y}) = \text{const.}
\end{aligned} \tag{B4}$$

The appropriate boundary conditions for closed cylindrical shells and cylindrically curved panels are the same as Eqs. (11) or Eqs. (12) except that here the conditions on ψ_1 and ψ_2 are not needed (since ψ_1 and ψ_2 do not appear in this thin-shell theory). Similarly, only the first three expressions in Eqs. (13) and the first three elements in Eqs. (15) are required.

Table 2. Geometric Parameters and Material-Property
Data for Example I (Ref. 8)

<u>Geometric Parameters</u>	
Wall thickness h , in (mm)	0.02 (0.51)
Middle-surface radius R , in (mm)	2.481 (63.0)
Length L , in (mm)	31.5 (800)
<u>Material Properties (Boron-Epoxy)</u>	
Fiber-direction Young's modulus, psi (GPa)	31.0×10^6 (214)
Transverse Young's modulus, psi (GPa)	2.7×10^6 (18.6)
Major Poisson's ratio, dimensionless	0.28
In-plane and thickness shear moduli, psi (GPa) ^a	0.75×10^6 (5.17)
Specific gravity, dimensionless	2.05

^a The minor Poisson's ratio is assumed to be given by the reciprocal relation.

Table 3. Natural Frequencies Associated with Various Vibrational Modes for a Complete Cylindrical Shell of Boron-Epoxy (Example I)

No. of axial half waves, m	No. of circum. full waves, n	Natural Frequencies, Hz			
		Ref. 8 ^a TST	Present		
			TST	SDT	SDT wRI
1	1	532	534	533	534
	2	235	241	240	246
	3	253	260	256	257
	4	444	450	418	412
	5	714	721	751	823
	6	1047	1056	1057	1113
	7	1442	1453	1460	1536
	8	1897	1911	1941	2028
2	1	1287	1290	1290	1290
	2	676	683	682	682
	3	443	454	445	444
	4	497	509	480	505
	5	728	739	753	830
	6	1051	1063	1083	1135
	7	1442	1456	1489	1511
	8	1897	1913	1932	2020

^a The numerical values listed here were taken directly from the computer printout, rather than from the less accurate graphical presentation of Ref. 8, which was not plotted accurately.

TST: thin-shell theory

SDT: shear deformable theory

SDT wRI: shear deformable theory with rotatory inertia

Table 4. Geometric Parameters and Material-Property Data for Example II

<u>Geometric Parameters</u>	<u>Ex. IIA (Ref. 18)</u>	<u>Ex. IIB (Ref. 19)</u>
Panel aspect ratio (L/b)	1	1 to 5
Middle-surface radius/thickness (R/h)	31.25 to 312.5	40
<u>Material Properties</u>		
Fiber-direction Young's modulus	$40 E_T$	$25 E_T$
Transverse Young's modulus	E_T	E_T
Major Poisson's ratio ^a	0.25	0.25
In-plane and longitudinal-thickness shear moduli	E_T	$0.5 E_T$
Transverse-thickness shear modulus	$0.5 E_T$	$0.2 E_T$

^a The minor Poisson's ratio is assumed to be given by the reciprocal relation.

Table 5. Dimensionless Natural Frequencies $\omega b^2(P/E_T h^3)^{1/2}$ Associated with Various Vibrational Modes for Cylindrically Curved Panels (Example IIA)

No. of axial half waves m	No. of circ. half waves n	b/h	R/h	w/o Coupling ($B_{ij}=0$)		w/Coupling ($B_{ij} \neq 0$)	
				Ref. 18	Present	Ref. 18	Present
1	1	50	312.5	24.76	20.59	19.23	14.08
2	1	50	312.5	53.44	55.40	-	-
1	2	50	312.5	60.43	53.58	-	-
2	2	50	312.5	75.86	75.51	-	-
1	1	50	156.25	36.00	24.48	32.86	19.32
2	1	50	156.25	54.91	60.89	-	-
1	2	50	156.25	78.74	53.95	-	-
2	2	50	156.25	80.34	76.66	-	-
1	1	10	62.5	22.00	16.91	18.57	11.34
2	1	10	62.5	35.06	38.30	-	-
1	2	10	62.5	45.01	38.19	-	-
2	2	10	62.5	48.46	51.70	-	-
1	1	10	31.25	34.86	17.11	32.38	11.64
2	1	10	31.25	37.27	38.63	-	-
1	2	10	31.25	67.63	38.21	-	-
2	2	10	31.25	55.21	51.77	-	-

Table 6. Dimensionless Fundamental Frequencies $\omega b^2(P/E_T h^3)^{1/2}$
for Cylindrically Curved Panels (Example IIB)

Panel Aspect Ratio L/b	Without Coupling		With Coupling	
	Ref. 19	Present	Ref. 19	Present
1	16.11	15.89	11.71	11.65
2	10.94	10.79	7.35	7.37
3	10.27	10.10	6.58	6.59
4	10.07	9.91	6.32	6.33
5	9.99	9.83	6.22	6.21

Table 7. Material Properties for Aramid-Rubber Bimodulus
Composite Material^a

Property	k = 1	k = 2
Fiber-direction Young's modulus, GPa	3.58	0.0120
Transverse Young's modulus, GPa	0.00909	0.0120
Major Poisson's ratio, dimensionless	0.416	0.205
Minor Poisson's ratio, dimensionless	0.00106	0.205
In-plane and longitudinal-thickness shear moduli, GPa	0.00370	0.00370
Transverse-thickness shear modulus, GPa	0.00290	0.00499
Specific gravity, dimensionless	0.970	

^a Fiber-direction tension is denoted by k = 1, and fiber-direction compression by k = 2.

Table 8. Dimensionless Neutral-Surface Locations in the First and Second Portions of a Cycle for Two-Layer, Cross-Ply Cylindrical Panels Constructed of Aramid-Rubber (Sanders-Type Theory with Thickness Shear Deformation; $b/h = 10$)

Aspect ratio a/b	First Portion		Second Portion	
	$z_x^{(1)}$	$z_y^{(1)}$	$z_x^{(2)}$	$z_y^{(2)}$
<u>$R/h = 10$ (Highly Curved)</u>				
0.5	0.4405	-0.0987	-0.0272	0.3824
0.7	0.4343	-0.0736	-0.0374	0.4108
1.0	0.4234	-0.0521	-0.0546	0.4283
1.4	0.4069	-0.0368	-0.0768	0.4378
2.0	0.3796	-0.0250	-0.1101	0.4433
<u>$R/h = 20$ (Moderately Curved)</u>				
0.5	0.4430	-0.0827	-0.0226	0.4033
0.7	0.4387	-0.0618	-0.0316	0.4220
1.0	0.4312	-0.0438	-0.0459	0.4338
1.4	0.4195	-0.0311	-0.0648	0.4401
2.0	0.3995	-0.0213	-0.0930	0.4439
<u>$R/h = 50$ (Slightly Curved)</u>				
0.5	0.4446	-0.0719	-0.0193	0.4161
0.7	0.4418	-0.0539	-0.0272	0.4289
1.0	0.4361	-0.0384	-0.0394	0.4371
1.4	0.4276	-0.0273	-0.0558	0.4414
2.0	0.4130	-0.0190	-0.0801	0.4441

Table B-1 Thin-shell-theory tracers and their values

Theory	C_1	C_2	C_3	C_4
Sanders	1	1	3/2	1/2
Love's first approximation	1	1	1	0
Loo	1	0	1	0
Morley	1	0	0	0
Donnell	0	0	0	0

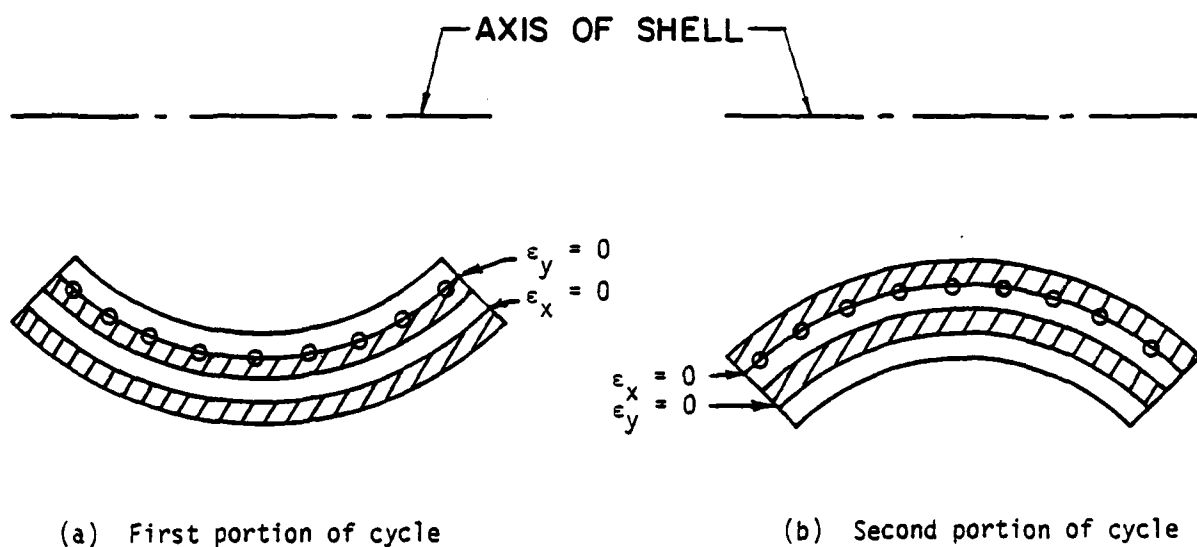


Fig. 2 Bimodulus action during the two portions of motion of a two-layer, cross-ply shell in the fundamental mode of vibration. Inside layer is in y direction (90°); outside layer is in x direction (0°). Shaded portions are in tension in the respective fiber directions.

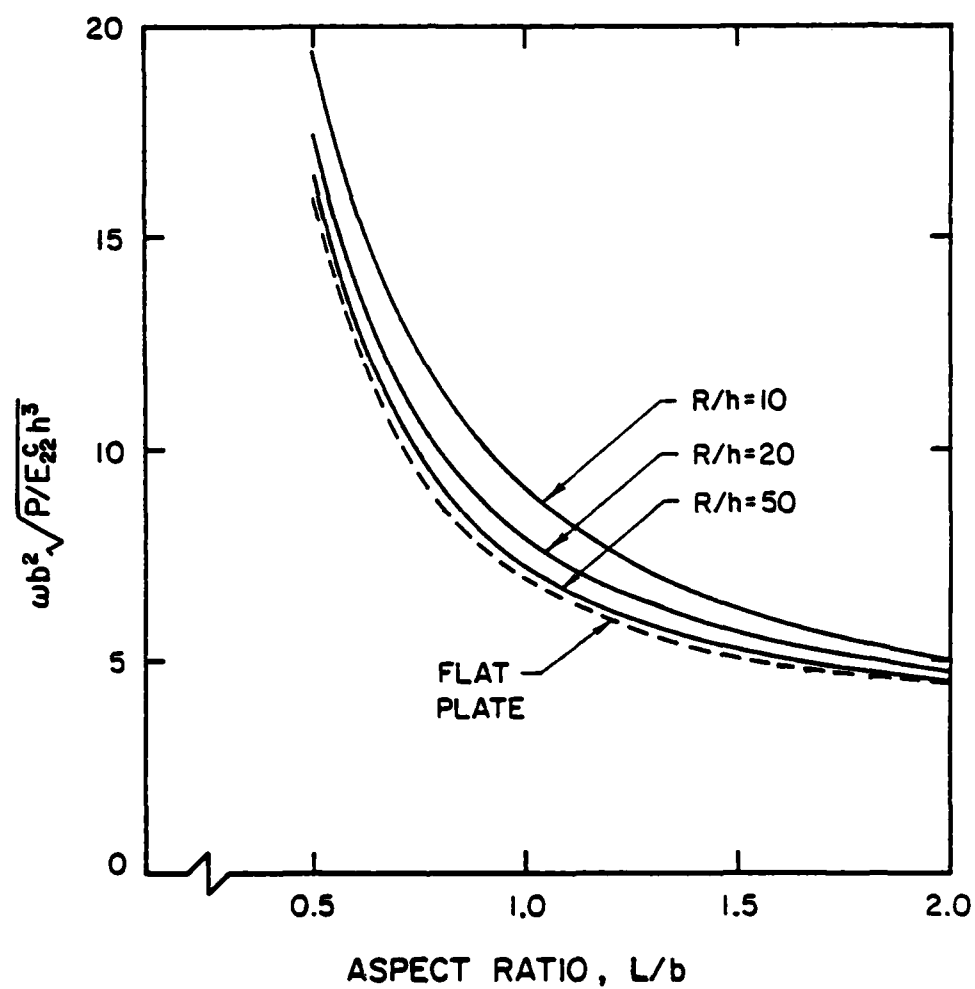


Fig. 3 Variation of fundamental frequency with aspect ratio for two-layer, cross-ply curved panels of aramid-rubber.

PREVIOUS REPORTS ON THIS CONTRACT

Project Rept. No.	OU-AMNE Rept. No.		Author(s)
1	79-7	Mathematical Modeling and Micromechanics of Fiber-Reinforced Bimodulus Composite Material	C.W. Bert
2	79-8	Analyses of Plates Constructed of Fiber-Reinforced Bimodulus Materials	J.N. Reddy and C.W. Bert
3	79-9	Finite-Element Analyses of Laminated Composite-Material Plates	J.N. Reddy
4A	79-10A	Analyses of Laminated Bimodulus Composite-Material Plates	C.W. Bert
5	79-11	Recent Research in Composite and Sandwich Plate Dynamics	C.W. Bert
6	79-14	A Penalty Plate-Bending Element for the Analysis of Laminated Anisotropic Composite Plates	J.N. Reddy
7	79-18	Finite-Element Analysis of Laminated Bimodulus Composite-Material Plates	J.N. Reddy and W.C. Chao
8	79-19	A Comparison of Closed-Form and Finite-Element Solutions of Thick Laminated Anisotropic Rectangular Plates (With a Study of the Effect of Reduced Integration on the Accuracy)	J.N. Reddy
9	79-20	Effects of Shear Deformation and Anisotropy on the Thermal Bending of Layered Composite Plates	J.N. Reddy and Y.S. Hsu
10	80-1	Analyses of Cross-Ply Rectangular Plates of Bimodulus Composite Material	V.S. Reddy and C.W. Bert
11	80-2	Analysis of Thick Rectangular Plates Laminated of Bimodulus Composite Materials	C.W. Bert, J.N. Reddy, V.S. Reddy, and W.C. Chao
12	80-3	Cylindrical Shells of Bimodulus Composite Material	C.W. Bert and V.S. Reddy
13	80-6	Vibration of Composite Structures	C.W. Bert
14	80-7	Large Deflection and Large-Amplitude Free Vibrations of Laminated Composite-Material Plates	J.N. Reddy and W.C. Chao
15	80-8	Vibration of Thick Rectangular Plates of Bimodulus Composite Material	C.W. Bert, J.N. Reddy, W.C. Chao, and V.S. Reddy
16	80-9	Thermal Bending of Thick Rectangular Plates of Bimodulus Material	J.N. Reddy, C.W. Bert, Y.S. Hsu, and V.S. Reddy
17	80-14	Thermoelasticity of Circular Cylindrical Shells Laminated of Bimodulus Composite Materials	Y.S. Hsu, J.N. Reddy, and C.W. Bert
18	80-17	Composite Materials: A Survey of the Damping Capacity of Fiber-Reinforced Composites	C.W. Bert

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM	
1. REPORT NUMBER OU-AMNE-80-20	2. GOVT ACCESSION NO. AD A0 92197	3. RECIPIENT'S CATALOG NUMBER	
4. TITLE (and Subtitle) VIBRATION OF CYLINDRICAL SHELLS OF BIMODULUS COMPOSITE MATERIALS		5. TYPE OF REPORT & PERIOD COVERED Technical Report No. 19	
		6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) C.W. Bert and M. Kumar		8. CONTRACT OR GRANT NUMBER(s) N00014-78-C-0647	
9. PERFORMING ORGANIZATION NAME AND ADDRESS School of Aerospace, Mechanical and Nuclear Engineering University of Oklahoma, Norman, OK 73019		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 064-609	
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy, Office of Naval Research Structural Mechanics Program (Code 474) Arlington, Virginia 22217		12. REPORT DATE October 1980	
		13. NUMBER OF PAGES 29	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED	
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; distribution unlimited.			
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)			
18. SUPPLEMENTARY NOTES To be presented at and appear in the Proceedings of the AIAA Dynamics Specialists Conference, Atlanta, Georgia, April 1981.			
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Bimodulus materials, composite materials, cylindrical shells, fiber-reinforced materials, laminates, natural frequencies, shell theory, vibration.			
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A theory is formulated for the small-amplitude free vibration of thick, circular cylindrical shells laminated of bimodulus composite materials, which have different elastic properties depending upon whether the fiber-direction strain is tensile or compressive. The theory used is the dynamic, shear deformable (moderately thick shell) analog of the Sanders best first approximation thin-shell theory. By means of tracers, the analysis can be reduced to various simpler shell theories, namely Love's first approximation, (over)			

DD FORM 1473
1 JAN 79EDITION OF 1 NOV 68 IS OBSOLETE
S/N 0102-014-6001UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. Abstract - Cont'd

and Donnell's shallow-shell theory. As an example of the application of the theory, a closed-form solution is presented for a freely supported panel or complete shell. To validate the analysis, numerical results are compared with existing results for various special cases. Also, the effects of the various shell theories, thickness shear flexibility, and bimodulus action are investigated.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

END

DATE
FILMED

8/

DTIC