

AD-A099 408

GEO-CENTERS INC NEWTON UPPER FALLS MA  
APPLICATION OF OPTICAL FIBERS TO DNA'S TESTING PROGRAM.(U)  
OCT 80 T C MAGUIRE, L ISAACSON  
GC-TR-80-1041

F/6 20/6


DNA001-79-C-0064

DNA-5478F

NL

UNCLASSIFIED

1-1  
AD  
A099408

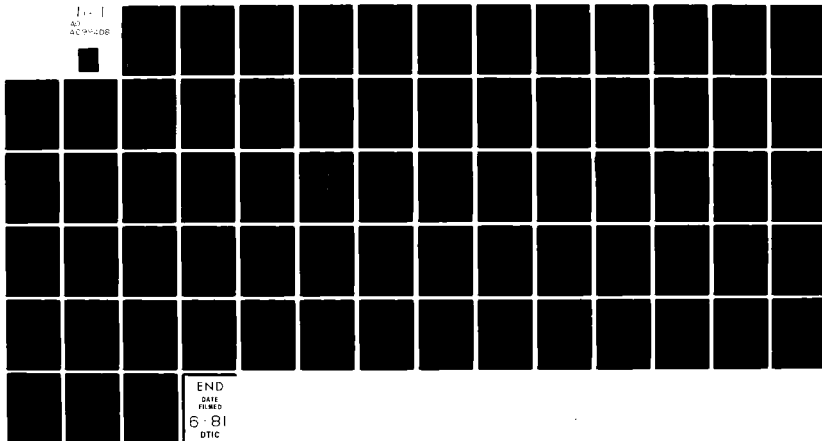

END  
DATE  
FILMED  
6-81  
DTIC

AD A099408

LEVEL 4

12

DNA 5478F

# APPLICATION OF OPTICAL FIBERS TO DNA'S TESTING PROGRAM

Thomas C. Maguire  
Louis Isaacson  
Geo-Centers, Inc.  
381 Elliot Street  
Newton Upper Falls, Massachusetts 02164

15 October 1980

Final Report for Period 1 November 1978—1 July 1980

CONTRACT No. DNA 001-79-C-0064

APPROVED FOR PUBLIC RELEASE;  
DISTRIBUTION UNLIMITED.

DTIC  
SELECTED  
MAY 27 1981

A

THIS WORK SPONSORED BY THE DEFENSE NUCLEAR AGENCY  
UNDER RDT&E RMSS CODE B345079462 J11AAXAX01311 H2590D.

Prepared for  
Director  
DEFENSE NUCLEAR AGENCY  
Washington, D. C. 20305

DTIC FILE COPY

81 5 27 040

Destroy this report when it is no longer  
needed. Do not return to sender.

PLEASE NOTIFY THE DEFENSE NUCLEAR AGENCY,  
ATTN: STTI, WASHINGTON, D.C. 20305, IF  
YOUR ADDRESS IS INCORRECT, IF YOU WISH TO  
BE DELETED FROM THE DISTRIBUTION LIST, OR  
IF THE ADDRESSEE IS NO LONGER EMPLOYED BY  
YOUR ORGANIZATION.



UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| 19 REPORT DOCUMENTATION PAGE                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                     |                                                                                                                       | READ INSTRUCTIONS<br>BEFORE COMPLETING FORM                                               |                                                      |
|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------|------------------------------------------------------|
| 18                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               | 1. REPORT NUMBER<br>DNA 5478F                                                                                         | 2. GOVT ACCESSION NO.<br>AD-A099 408                                                      | 3. RECIPIENT'S CATALOG NUMBER                        |
| 6                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                | 4. TITLE (and Subtitle)<br>APPLICATION OF OPTICAL FIBERS TO DNA'S<br>TESTING PROGRAM                                  | 5. TYPE OF REPORT & PERIOD COVERED<br>Final Report, for Period<br>1 Nov 1978 - 1 Jul 1980 | 6. PERFORMING ORG. REPORT NUMBER<br>GC-TR-80-1041    |
| 10                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               | 7. AUTHOR(s)<br>Thomas C./Maguire<br>Louis/Isaacson                                                                   | 8. CONTRACT OR GRANT NUMBER(s)<br>DNA 001-79-C-0064                                       |                                                      |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  | 9. PERFORMING ORGANIZATION NAME AND ADDRESS<br>Geo-Centers, Inc.<br>381 Elliot Street<br>Newton Upper Falls, MA 02164 | 10. PROGRAM ELEMENT, PROJECT, TASK<br>AREA & WORK UNIT NUMBERS<br>Subtask J11AAXA013-11   |                                                      |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  | 11. CONTROLLING OFFICE NAME AND ADDRESS<br>Director<br>Defense Nuclear Agency<br>Washington, D.C. 20305               | 12. REPORT DATE<br>15 October 1980                                                        | 13. NUMBER OF PAGES -<br>70                          |
| 17                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               | 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)<br>X013                                   | 15. SECURITY CLASS. (cf this report)<br>UNCLASSIFIED                                      | 15a. DECLASSIFICATION/DOWNGRADING<br>SCHEDULE<br>N/A |
| 16. DISTRIBUTION STATEMENT (of this Report)<br><br>Approved for public release; distribution unlimited.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |                                                                                                                       |                                                                                           |                                                      |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |                                                                                                                       |                                                                                           |                                                      |
| 18. SUPPLEMENTARY NOTES<br><br>This work sponsored by the Defense Nuclear Agency<br>under RDT&E RMSS Code B345079462 J11AAXA01311 H2590D.                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        |                                                                                                                       |                                                                                           |                                                      |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number)<br><br>Fiber Optics<br>Underground Nuclear Tests<br>Data Transmission                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |                                                                                                                       |                                                                                           |                                                      |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number)<br><br>Recent advances in the field of fiber optics communications and the development of fiber optic cabling systems represent a technological breakthrough that offers significant advantages over conventional coaxial cabling systems. The advantages of fiber optic systems include lightweight, wide bandwidth, freedom from electromagnetic interference (EMI) and groundloops, and immunity to crosstalk and short circuit loading. Different applications capitalize on those advantages most attractive to the user. The application |                                                                                                                       |                                                                                           |                                                      |

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

410271

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

of fiber optics to nuclear weapons effects tests sponsored by the Defense Nuclear Agency (DNA) is the topic of this report.

Since 1977, experiments utilizing fiber optics have been fielded in underground nuclear tests. Early applications involved experiments designed to characterize fibers in the underground testing environment. The success of these early measurements has developed confidence in fibers to the point of fielding non-redundant fiber optic links, thus, taking full advantage of their useful characteristics.

The encouraging results of testing fiber optic systems to date certainly justifies the continued interest in their use in underground nuclear testing and other applications involving severe environments. The all-dielectric construction of fiber cables makes them lightweight and eliminates many grounding and shielding problems. The wide bandwidth of the fibers enhances the multiplexing capabilities making it possible to reduce the total number of cables. This simplifies the cabling of an event and also has a significant economic impact.

In addition to benefitting UGT, advances in fiber optic technology can greatly impact other DNA activities such as hardening of military components and simulation and testing in high radiation environments. Using the UGT environment as a test bed, optical fibers can be characterized in severe radiation and stress environments. Due to the importance of optical fiber characteristics and the potential benefits from their use, it is recommended that DNA take a lead role in the research and development of fiber optic technology for use in adverse test and simulation environments.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

## PREFACE

The authors wish to thank Dr. George Sigel of the Naval Research Laboratory and Dr. Pete Lyons of the Los Alamos Scientific Laboratory for their comments and suggestions. The assistance provided by Mr. Noel Gantick of the DNA Field Command and our COR, Mr. R. C. Webb, is also gratefully acknowledged.

[illegible]

## TABLE OF CONTENTS

| <u>Section</u>                                                | <u>Page</u> |
|---------------------------------------------------------------|-------------|
| PREFACE                                                       | 1           |
| LIST OF ILLUSTRATIONS                                         | 3           |
| LIST OF TABLES                                                | 4           |
| 1 INTRODUCTION                                                | 5           |
| 2 CURRENT DNA EXPERIMENTS AND PRESENT<br>CABLING REQUIREMENTS | 8           |
| 2-1 TYPES OF MEASUREMENTS                                     | 8           |
| 2-2 PHYSICAL LAYOUT OF EXPERIMENTS                            | 11          |
| 2-3 CABLING REQUIREMENTS                                      | 11          |
| 2-3.1 Grounding and Shielding Requirements                    | 13          |
| 3 FIBER OPTICS PRINCIPLES AND CHARACTERISTICS                 | 18          |
| 3-1 PRINCIPLES OF OPTICAL WAVEGUIDES                          | 18          |
| 3-2 FIBER CHARACTERISTICS                                     | 23          |
| 3-2.1 Fiber Materials                                         | 23          |
| 3-2.1.1 Synthetic Silica Fibers                               | 23          |
| 3-2.1.2 Polymer Clad Silica<br>(PCS Fibers)                   | 23          |
| 3-2.1.3 Complex Silicate Glass Fibers                         | 23          |
| 3-2.1.4 All Plastic Fibers                                    | 24          |
| 3-2.2 Mechanical Considerations                               | 24          |
| 3-2.2.1 Minimum Bend Radius                                   | 24          |
| 3-2.2.2 Tensile Strength                                      | 27          |
| 3-2.2.3 Microbending                                          | 27          |
| 3-2.3 Optical Properties                                      | 27          |
| 3-2.3.1 Attenuation                                           | 27          |
| 3-2.3.2 Distortion                                            | 30          |
| 3-2.4 Radiation Sensitivity                                   | 32          |
| 3-3 FIBER OPTIC SYSTEMS                                       | 33          |
| 3-3.1 Active System Design                                    | 37          |
| 4 USE OF FIBERS IN UGT                                        | 47          |
| 4-1 ADVANTAGES OF FIBERS FOR UGT                              | 47          |
| 4-2 DIAGNOSTIC APPLICATIONS                                   | 50          |
| 4-3 EFFECTS MEASUREMENT APPLICATIONS                          | 53          |
| 4-4 FUTURE USES OF FIBERS IN UGT                              | 58          |
| 5 CONCLUSIONS AND RECOMMENDATIONS                             | 59          |
| 6 REFERENCES                                                  | 61          |

## LIST OF ILLUSTRATIONS

| <u>Figure</u> |                                                                                                                       | <u>Page</u> |
|---------------|-----------------------------------------------------------------------------------------------------------------------|-------------|
| 1             | Layout of test tunnel at the Nevada Test Site                                                                         | 12          |
| 2             | Zero-time noise sources                                                                                               | 15          |
| 3             | Guided and unguided rays of light in fiber optic waveguides                                                           | 19          |
| 4             | Refractive index profiles for three categories of optical fibers                                                      | 21          |
| 5             | Modal distortion within optical fiber waveguides                                                                      | 22          |
| 6             | Cross section of SIECOR cable                                                                                         | 28          |
| 7             | Typical attenuation loss from a high-silica optical fiber without dopants                                             | 29          |
| 8             | Comparison of coaxial cable and fiber optic attenuation                                                               | 31          |
| 9             | Total loss in optical fiber waveguides as a function of dose during in situ steady state $^{60}\text{Co}$ irradiation | 35          |
| 10            | Decay of radiation-induced optical attenuation following a dose of electrons                                          | 35          |
| 11            | Block diagram of an optical transmission link                                                                         | 38          |
| 12            | Loss spectra of fibers for long wavelength operation                                                                  | 42          |
| 13            | Loss budget for fiber transmission links                                                                              | 44          |
| 14            | Range of bandwidth-distance products                                                                                  | 45          |
| 15            | Schematic of a typical NTS rack geometry                                                                              | 52          |
| 16            | Typical strain gauge bridge configurations                                                                            | 55          |
| 17            | Strain gauge data transmitted on coaxial cable                                                                        | 56          |
| 18            | Strain gauge data transmitted on fiber optic cable                                                                    | 57          |

## LIST OF TABLES

| <u>Table</u> |                                                                                                                     | <u>Page</u> |
|--------------|---------------------------------------------------------------------------------------------------------------------|-------------|
| 1            | Advantages of fiber optics                                                                                          | 7           |
| 2            | Typical measurements made during an underground test                                                                | 9           |
| 3            | Typical UGT bandwidth requirements                                                                                  | 10          |
| 4            | Cables available in the uphole cable run for Diablo Hawk                                                            | 14          |
| 5            | Characteristics of commercially available fibers                                                                    | 25          |
| 6            | Characteristics of commercially available fiber optic cables                                                        | 26          |
| 7            | Key parameters in the radiation damage of fibers                                                                    | 34          |
| 8            | System requirements, fiber behavior, and candidate fibers for optical communication systems in nuclear environments | 36          |
| 9            | Commercially available optical transmitters                                                                         | 39          |
| 10           | Commercially available optical receivers                                                                            | 40          |
| 11           | Long wavelength source and detector materials                                                                       | 41          |
| 12           | Comparison of high quality coax cable and SIECOR optical fiber cable                                                | 48          |

## SECTION 1

### INTRODUCTION

The Defense Nuclear Agency (DNA) is charged by the Joint Chiefs of Staff with the responsibility to conduct nuclear weapons effects tests. These tests, conducted underground at the Nevada Test Site (NTS), demand sophisticated state-of-the-art systems designed to measure both the physical effects and the radiation output (diagnostics) of the nuclear device. Because of the hostile environment, the specialized nature of the source, and the large quantities of data required, many highly developed technologies often unique to this program, are needed to ensure a successful test. Further, advances in any of these technologies can have a significant impact upon the quality, quantity, and the economy of data collection and the ability to adequately quantify the measured effects.

Recent advances in the field of fiber optics communication (data transmission) represent a technological breakthrough which can offer significant advantages to underground testing (UGT). Data transmission from the experiments to the remotely located recording stations currently requires many runs of long lengths of metallic cables which present problems and limitations inherent with their use. The procurement and handling costs of these cables represent a significant fraction of the total cost of an underground test. The number of experiments and the bandwidth are severely limited by inherent metallic cable properties. Further, the logistics and reliability of grounding and shielding metallic cables in a high radiation background (both nuclear and electromagnetic) has long been a major problem in UGT programs.

Optical fiber technology offers substantial and fundamental advantages over conventional cables used for data communication systems. Several of these advantages are listed in Table 1. Different applications capitalize on those advantages most attractive to the user. Recent advances in the technology have been brought about by research efforts in support of the communications industry, principally the telephone companies. There, the lightweight and high bandwidth are particularly attractive.

For UGT, several of the advantages of fiber optics over metallic cables make their use attractive. The problems encountered in UGT due to the use of coax and other conventional cables can be lessened, if not eliminated, with the use of an all-dielectric, lightweight transmission link. The application of fiber optics to DNA sponsored UGT is the topic of this report.

An overview of a typical DNA-sponsored underground test is given in Section 2 where the requirements for data transmission and cabling are reviewed. In Section 3, fiber optic principles and characteristics are discussed. Section 4 is a summary of UGT measurements which have, to date, employed fiber optics. Demonstrated advantages of fiber optic waveguides for the UGT environment are given. Finally, in Section 5, areas are identified which should be explored in order to take maximum advantage of the capabilities provided by fiber optic technology in the UGT program.

Table 1. Advantages of fiber optics.

Wide Bandwidth  
Freedom from Groundloops  
Immune to Crosstalk  
Freedom from Electromagnetic Interference (EMI)  
Lightweight  
Transmission Security  
Immunity to Jamming  
Immunity to Short Circuit Loading  
Chemical Resistance  
Use of Non-Strategic Materials

## SECTION 2

### CURRENT DNA EXPERIMENTS AND PRESENT CABLING REQUIREMENTS

Nuclear weapons effects are phenomena which are produced and given off by the explosion of a nuclear device and which interact with the surrounding environment or the materials to be exposed. The weapons effects normally consist of X-ray, gamma, and neutron radiations, as well as Electromagnetic Pulse (EMP), blast, and shock. The nuclear device is provided to the DNA by one of the weapons laboratories, i.e., the Lawrence Livermore Laboratory (LLL) or the Los Alamos Scientific Laboratory (LASL).

#### 2-1 TYPES OF MEASUREMENTS.

While many types of measurements are taken during these tests, they can be divided into two broad categories: effects and diagnostic. Table 2 lists the various types of gauges that were fielded for a recent event, code named DIABLO HAWK (Ref. 1). The number of channels of each type of measurement is also given in the table. The required bandwidth for each type of measurement is given in Table 3. The strain measurements and most other effects measurements have relatively low frequency requirements (<20 kHz), while the diagnostic measurements require much higher bandwidth instrumentation systems (up to 1 GHz).

Table 2. Typical measurements made during an underground test.

| <u>Measurement<br/>Parameter</u> | <u>Number of<br/>Channels</u> |
|----------------------------------|-------------------------------|
| Velocity                         | 242                           |
| Acceleration                     | 80                            |
| Strain                           | 553                           |
| Stress                           | 128                           |
| Break Wire                       | 330                           |
| Make Wire                        | 50                            |
| Sliffer                          | 10                            |
| Pressure                         | 421                           |
| Time Domain Reflectometer        | 2                             |
| Thermocouple                     | 109                           |
| Impulse                          | 32                            |
| Time Resolved Impulse            | 28                            |
| Time Resolved Momentum           | 16                            |
| Calorimeters                     | 48                            |
| Carbon                           | 15                            |
| Quartz                           | 35                            |
| Compton Diodes                   | 23                            |
| Photo Diodes                     | 18                            |
| XRD                              | 62                            |
| Current Sensors (EMP)            | <u>127</u>                    |
| Total Channels                   | 2329                          |

Table 3. Typical UGT bandwidth requirements.

| <u>Measurement<br/>Parameter</u> | <u>Signal Frequency<br/>Range</u> |
|----------------------------------|-----------------------------------|
| Velocity                         | <20 KHz                           |
| Acceleration                     | <20 KHz                           |
| Strain                           | <20 KHz                           |
| Stress                           | <20 KHz                           |
| Break Wire                       | <20 KHz                           |
| Make Wire                        | <20 KHz                           |
| Sliffer                          | <20 KHz                           |
| Pressure                         | <20 KHz                           |
| Time Domain<br>Reflectometer     | < 5 MHz                           |
| Thermocouple                     | <20 KHz                           |
| Impulse                          | <40 KHz                           |
| Time Resolved Impulse            | <50 MHz                           |
| Time Resolved Momentum           | <50 MHz                           |
| Calorimeters                     | <50 MHz                           |
| Carbon                           | <50 MHz                           |
| Quartz                           | <50 MHz                           |
| Compton Diodes                   | <100 MHz                          |
| Photo Diodes                     | <100 MHz                          |
| XRD                              | <500 MHz                          |
| Current Sensors (EMP)            | < 1 GHz                           |

## 2-2 PHYSICAL LAYOUT OF EXPERIMENTS.

The layout for a typical, DNA sponsored underground effects test is shown in Figure 1. The tests are conducted in tunnels drilled into the side of Rainer Mesa at the NTS. The tunnels extend, horizontally, about one mile into the mesa at an overburden depth of 1000 to 1500 feet.

Pipes containing the experimental gauges are placed into drifts that extend from the nuclear device down the tunnel as far as 1000 feet. The pipes are designed to be gas tight and are evacuated during the test. Experiments are mounted on bulkheads placed across the pipe at several locations along its length. This provides several levels of radiation exposure. Signal cables from the individual experiments are routed behind the bulkheads and through the pipe walls at vacuum ports. From the vacuum ports, they go to instrumentation alcoves. These alcoves are generally located within 100 to 300 feet of the experimental station and are used for conditioning the data signals prior to transmitting them to the recording station. Recording stations are located both underground and at the mesa surface.

## 2-3 CABLING REQUIREMENTS.

Long lengths of cable are required for data transmission due to the remote monitoring of underground test measurements. Typical cable lengths from transducer to recording system can vary from 1000 to 5500 feet (Ref. 2). In all, more than 800 miles of cable can be used for instrumenting a typical event. More than half of the cable laid is not reused. For example, approximately 480 miles of cable, with procurement costs approaching \$633,000 (Ref. 3) will be laid underground for use on the MINOR's IRON event planned for fall 1980.

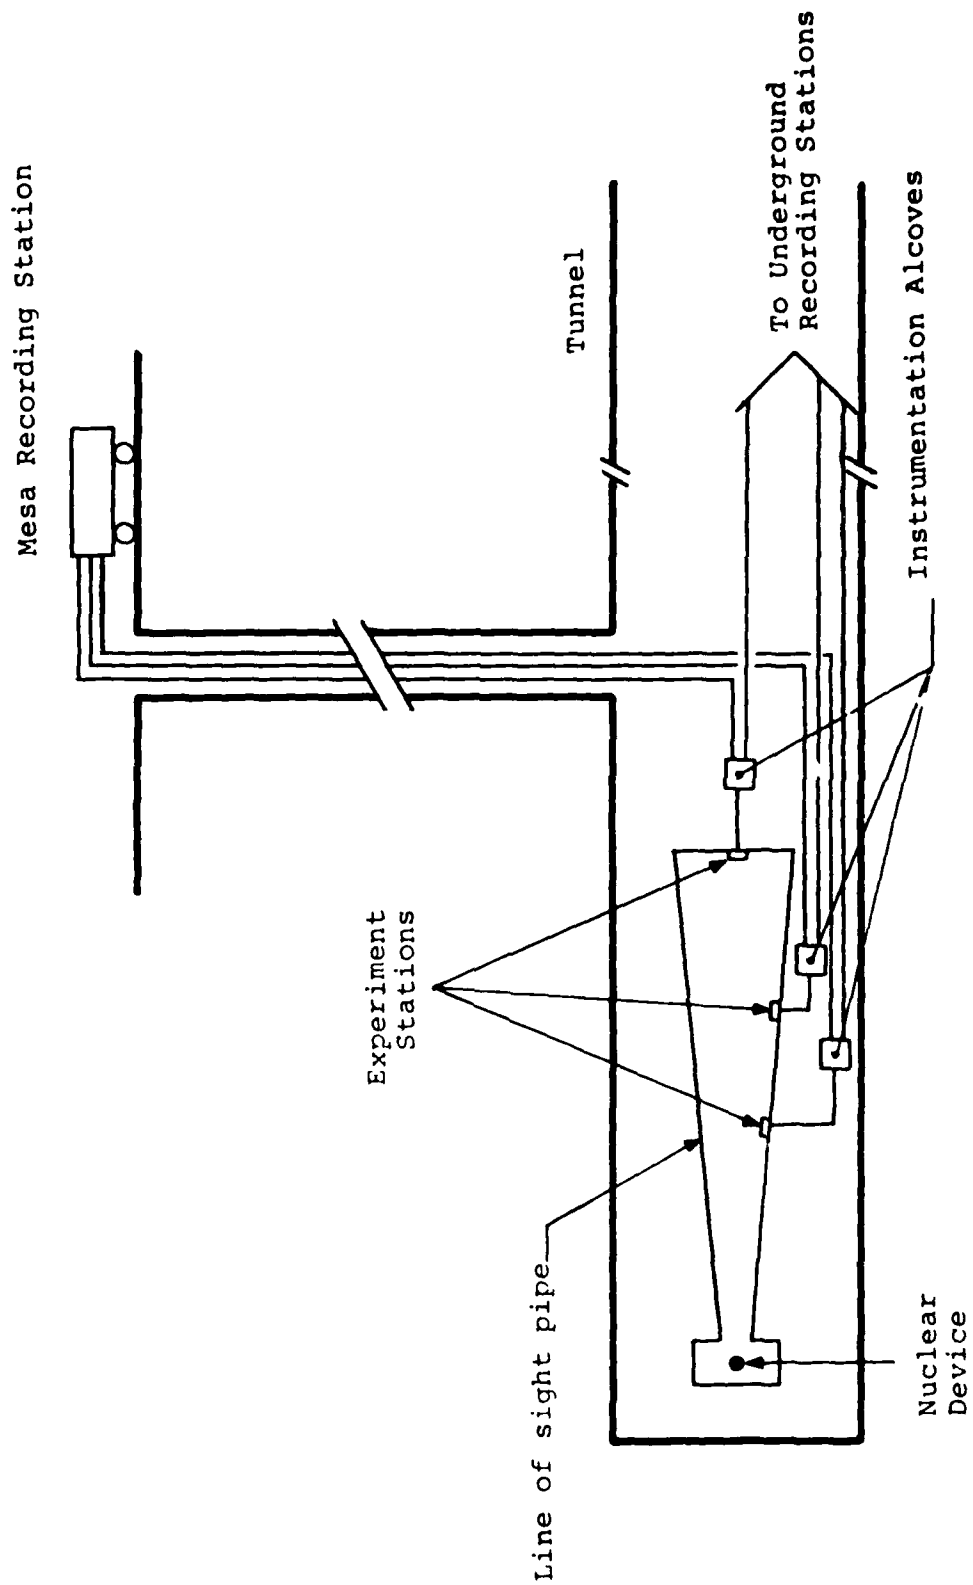


Figure 1. Layout of test tunnel at the Nevada Test Site. (Ref. 5)

Data transmitted to recording stations on the mesa surface are routed through the cable runs which are reused for each event. This link, then, limits the number of data channels which can be recorded uphole. Tests are performed on the cable plant before each event to determine which cables are usable. The listing shown in Table 4 gives the cables that were available in the main uphole cable plant for the DIABLO HAWK event (Ref. 1).

The type of cable utilized for each measurement is determined by several factors: signal requirements (frequency response, signal to noise ratio, etc), environmental parameters (radiation field, temperature, pressure, etc.), and grounding and shielding requirements for electromagnetic interference (EMI) suppression. Frequency response requirements for various gauges were given in Table 3. Environmental parameters vary along the length of the cable. For example, the radiation dose rates vary from approximately  $10^{13}$  rad/sec (prompt gamma) at 3 meters from the source to background at the recording station (Ref. 4). Grounding and shielding requirements are overviewed in the following discussion.

#### 2-3.1 Grounding and shielding requirements.

A major problem in fielding UGT experiments is the electrical overload and the consequent data loss from zero-time electrical noise in the measuring system. A model describing the zero-time noise identifies three sources that predominate (Ref. 5). These sources, illustrated in Figure 2, are outlined below:

1. - Photon induced surface emission of electrons for the experiment structure, pipe, and bulkhead.
2. - Photon induced charge transfer within the cables that are internal to the pipe.
3. - Induced noise in the cable system between transducer and recording system.

Table 4. Cables available in the uphole cable run for DIABLO HAWK  
(Ref. 1)

| <u>Cable Type</u>     | <u>Number Available</u> |
|-----------------------|-------------------------|
| Twisted Shielded Pair | 1403                    |
| RG331                 | 146                     |
| RG213                 | 80                      |
| RG333                 | 34                      |
| RG22B                 | 20                      |
| RG215                 | 20                      |



Source number 3 is the most conventional and is present to some extent in any large cable system. It is, essentially, the impulse response of the cable plant.

Of great concern are the noise-induced signals that are allowed to propagate throughout the cable plant and couple into signal cables. There are several mechanisms that allow signals on the cable shields to penetrate into the cable. Cable conductors and splices are potential ports of entry for Radio Frequency (RF) noise. Also, braided cable shields leak electrically at frequencies above 100 MHz, with a coupling coefficient that is a function of the braid spacing. At lower frequencies, (i.e., less than 100 MHz), the cable shield is shallow compared to the skin depth of several millimeters. This allows signal coupling that is a function of the shield transfer impedance.

To overcome zero-time data loss, a large effort is put into grounding and shielding the instrumentation. Grounding and shielding requirements impose restrictions on cable selection and splicing, in addition to gauge design. Historically, experimenters have adopted systems based upon non-UGT recording environments as well as trial and error methods that have succeeded on previous tests. Recent efforts have been directed toward adopting a unified grounding and shielding plan to be followed by experimenters. (Ref. 4)

To insure against radioactive gas leakage to the atmosphere, gas blocks are installed in the cables used to transmit the data. For twisted shielded pair cable, such as might be used for low-level analog signals, gas blocks are constructed by separating the conductors and shields into individual wires and filling the area around the wires with epoxy. This results in a break in shield integrity and introduces a severe noise injection point for this type of cable.

In summary, a significant effort goes into planning the cabling for each underground test. The problems and limitations inherent in the use of bulky, metallic cables complicate the instrumentation of an event. These complications provide a tremendous incentive to develop all-dielectric, lightweight, data transmission links, such as those utilizing fiber optic waveguides. Recent developments, principles, and characteristics of optical fiber transmission links are discussed in the next section.

### SECTION 3

#### FIBER OPTICS: PRINCIPLES AND CHARACTERISTICS

##### 3-1 PRINCIPLES OF OPTICAL WAVEGUIDES

The theory governing optical waveguiding is derived from a straightforward application of Snell's Law. From this law of optics, the path of a ray of light can be determined in a refracting material from the following equation:

$$n_1 \sin \theta_1 = n_2 \sin \theta_2 \quad (1)$$

The parameters are defined in Figure 3. The condition for optical waveguiding occurs whenever  $\theta_2 \geq 90^\circ$ , i.e. total internal reflection. This defines a critical angle of incidence,  $\theta_{1c}$ , necessary for total reflection given by:

$$\theta_{1c} = \sin^{-1} \left( \frac{n_2}{n_1} \right) \quad (2)$$

For  $\theta_1 < \theta_{1c}$ , the light ray will escape into the cladding. The principle of total internal reflection is utilized in light communications by constructing a cladded fiber with a core material having a larger index of refraction than the cladding material, i.e.  $n_{\text{core}} > n_{\text{clad}}$ , or in terms of the parameters defined in Figure 3,  $n_1 > n_2$ .

A characteristic parameter of optical fibers is the numerical aperture, NA. The NA is meant to serve as a measure of the light gathering ability of the fiber. Quantitatively, it is given by:

$$NA = \sin (\phi/2) \quad (3)$$

The angle,  $\phi/2$ , (see Figure 3), is the maximum angle between the fiber axis and a light ray that will be guided along the fiber.

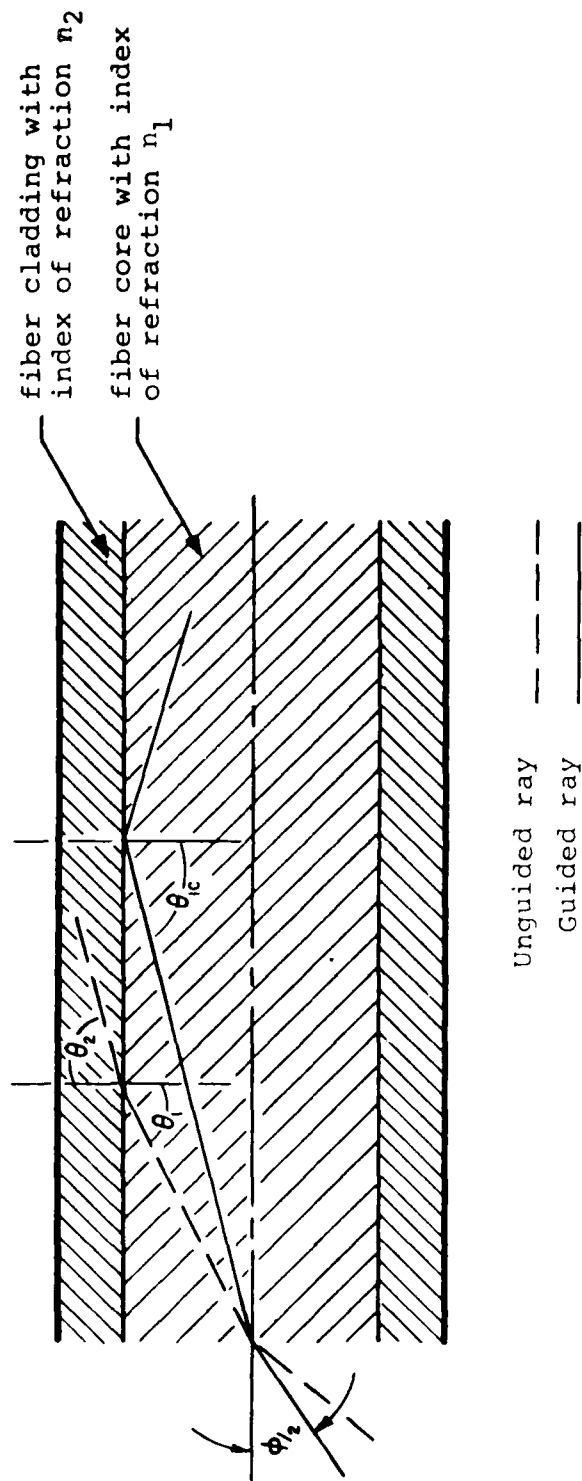


Figure 3. Guided and unguided rays of light in fiber optic waveguides.

The cone of light that will be accepted and guided along the fiber is characterized by the included angle,  $\phi$ .

Propagating electromagnetic waves give rise to guided and unguided modes within the fiber. For any fiber waveguide of finite size, only a finite number of wave modes will be guided at a given optical frequency. Guided modes are the only ones of interest since they are confined by the fiber.

There are three broad categories of optical fibers:

1. Single Mode Step Index
2. Multimode Step Index
3. Multimode Graded Index

The three categories are illustrated qualitatively in Figure 4. In step index fibers, the index of refraction,  $n$ , is constant across the fiber core diameter, while in graded index fibers,  $n$  tapers continuously from the center axis value,  $n_1$ , to a lower value,  $n_2$ , at the end of the fiber radius.

Light paths for guided rays are illustrated in Figure 5. The single mode step index fiber has a small core diameter and a single mode is sustained. Larger diameter step index fibers allow more modes to be sustained. Since high angle rays travel a greater distance for a given length of fiber than lower angle ones, a pulse broadening occurs. A narrow pulse of light slowly broadens in time as it travels down the fiber, ultimately limiting the bandwidth of the fiber.

The advantage of the multimode fiber over the single mode is its larger numerical aperture. Multimode graded index fibers provide a means of utilizing this advantage and minimizing the pulse broadening. In this type of fiber, the smooth change in refractive index radially from the center of the fiber effectively decreases the path length difference between low and high order modes as

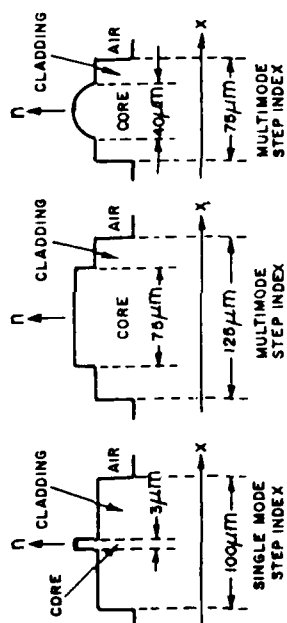


Figure 4. Refractive index profiles for three categories of optical fibers.

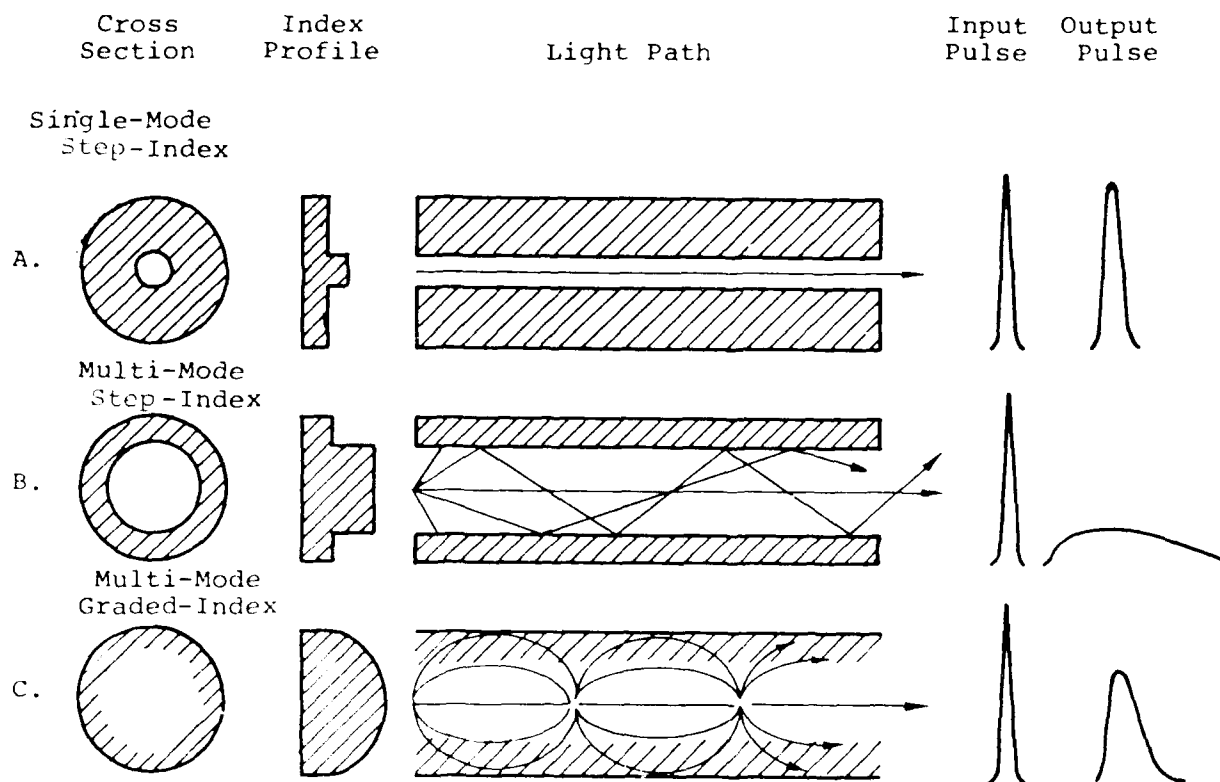


Figure 5. Modal Dispersion within optical fiber waveguides.

illustrated in Figure 5. In addition, the high angle rays now travel much of the time in a material with a lower index of refraction. As the index of refraction decreases, the velocity of propagation increases, decreasing the pulse spread even more.

### 3-2 FIBER CHARACTERISTICS.

#### 3-2.1 Fiber Materials.

Four general classes of fibers are commercially available. The materials used and the method of preparation determine the mechanical and optical properties of the finished fiber. The general classes are described below.

3-2.1.1 Synthetic Silica Fibers. These all glass fibers are high purity and comprise the group with the lowest optical losses (attenuation). Some manufacturers dope the silica ( $\text{SiO}_2$ ) cores and/or cladding with germanium (Ge), boron (B), phosphorous (P), or other material in order to obtain desired core/clad indices of refraction.

3-2.1.2 Polymer Clad Silica (PCS) Fibers. Glass fibers drawn from high purity synthetic silica rods are dip coated in a plastic or silicone solution and receive a thick protective polymer jacket to form a low cost, durable optical fiber waveguide. PCS fibers can support larger cores than all glass fibers without becoming brittle because of their plastic cladding. Since the cladding and core are made of dissimilar materials, however, PCS fibers are inherently step-index fibers.

3-2.1.3 Complex Silicate Glass Fibers. Virtually all of the early glass fiber optic waveguides were fabricated using lead silicate glass cores and borosilicate or soda-lime silicate glass cladding. The high index of refraction of the core, due to the presence of lead, results in a high numerical aperture and, therefore, very efficient coupling to a light source.

3-2.1.4 All Plastic Fibers. Fibers offering excellent mechanical properties near room temperature are fabricated from materials such as polymethylmethacrylate (PMMA) and polystyrene. These all plastic fibers do not suffer the brittle fracture problems of glasses, but exhibit the highest intrinsic optical losses of the four classes of fibers.

Several examples of each class of fibers are given in Table 5 along with manufacturers, characteristic loss properties, numerical aperture and bandwidth. Fibers are manufactured by a variety of techniques including chemical vapor deposition (CVD) processes, laser drawing processes, and compound melting. The processes and equipment used in fiber drawing can be found in the literature (Ref. 6, 7).

One or more optical fibers are incorporated into a cable structure for use in most systems. Cable structures provide environmental and mechanical protection, increased permissible tensile loading, and sizes convenient for handling. Examples of commercially available cables along with characteristic parameters and properties are listed in Table 6.

### 3-2.2 Mechanical Considerations.

The mechanical properties of the optical fiber cable can influence its ability to transmit optical information. Specifically, consideration must be given to the cable's strength and how tightly it can be bent in order not to degrade its signal handling capability.

3-2.2.1 Minimum Bend Radius. This is the smallest radius to which a cable is bent without placing the fiber under excessive mechanical stress. Bending the cable to a smaller radius causes coupling of an excessive number of propagating modes out of the core and into the cladding. In addition, stress cracks that actually shear the fiber

Table 5. Characteristics of commercially available fibers.

| Core Material | Cladding Material | Manufacturer        | Index Profile | Numerical Aperture | Bandwidth (MHz-Km) | Attenuation (db/Km @ $\lambda$ in nm) | Price (\$/m) |
|---------------|-------------------|---------------------|---------------|--------------------|--------------------|---------------------------------------|--------------|
| doped silica  | silica            | Fujikura Cable      | single        |                    | $10^4$             | .7 @ 1300                             |              |
| silica        | silica            | Corning Glass Works | graded        | .2                 | 400                | 2 @ 900                               | 1.40         |
| silica        | plastic           | Maxlight Optical    | step          | .41                | 24                 | <5 @ 820                              | 1.15         |
| glass         | glass             | Optronic Fort       | step          | .29                | 30                 | 10 @ 850                              | .95          |
| glass         | glass             | Quartz and Silica   | graded        | .16                | 200                | <15                                   |              |
| fused silica  | plastic           | Fiberoptic Cable    | step          | .25                | 25                 | 20 @ 820                              | .90          |
| silica        | silicone          | Quartz Prod/Q & S   | step          | .38                | 15                 | 50 @ 820                              | 1.50         |
| glass         | glass             | Optronic Fort       | step          | .48                | 20                 | 100 @ 850                             | .15          |
| plastic       | plastic           | Optronic Fort       | step          | .5                 | 10                 | 400 @ 850                             | .60          |
| acrylic       | fluorocarbons     | Poly-Optical Prods. | step          | .5                 |                    | 900                                   | .02          |

Table 6. Characteristics of commercially available fiber optic cables.

| Manufacturer      | Number of<br>Fibers | Cable dia.<br>(mm) | Weight<br>(kg/km) | Tensile<br>Strength (kg) | Min. Bend<br>Radius<br>(cm) | Bandwidth<br>(MHz-Km) | Attenuation<br>(dB/km @<br>$\lambda$ in nm) |
|-------------------|---------------------|--------------------|-------------------|--------------------------|-----------------------------|-----------------------|---------------------------------------------|
| Fujikura Cable    | 1-48                | 5-30               | 10-500            | 50-300                   | 5-36                        | 10 <sup>4</sup>       | 1.0 @ 1300                                  |
| Optronics Fort    | 4                   | 12                 |                   | 70                       | 20                          | 300                   | 4                                           |
| Times Fiber Comm. | 1-12                |                    |                   |                          |                             | 200-600               | 5 to 8                                      |
| Belden            | 6                   | 8                  | 40                | 140                      | 10                          | 20                    | 5 @ 850                                     |
| Maxlight Optical  | 1                   | 2.4                | 6                 | 80                       | .5                          | 24                    | <10 @ 630                                   |
| Optelecom         | 3                   | 3.5                | 21                | 200                      | 10                          | 20                    | 15 @ 800                                    |
| MERET             | 1                   | .6                 | 6                 | 30                       |                             | 50                    | 100 @ 900                                   |
| Siecor            | 6                   | 5.0                | 25                | 750                      | 2.5                         | 200                   | 20                                          |

and break the link are induced.

3-2.2.2 Tensile Strength. Tensile strength is especially important if the cable must be drawn through conduit or hang self-supported over long distances. Fiber optic cables always have some additional members that provide the strength needed in most applications. Most often they are made of dielectric material such as Kevlar which also maintains electrical isolation. Thus, it is the strength of these additional members that actually handles the tensile load.

3-2.2.3 Microbending. A significant factor in optical cable design is the optical loss caused by a phenomenon called microbending. When an optical fiber is deformed on a microscopic scale, coupling of propagating modes from the core to the clad becomes a problem. To overcome this, buffering of the fibers is accomplished either before or during cable manufacture.

An example of a ruggedized cable suitable for a variety of demanding applications is SIECOR General Purpose optical cable\* manufactured by SIECOR Optical Cables, Inc. A cross-section of the SIECOR cable is shown in Figure 6 (Ref. 8).

### 3-2.3 Optical Properties.

The optical properties of importance in fiber optic waveguides are attenuation and distortion. Both impact on the usable length of the fiber and on the bandwidth of the system. The influence of other components of the fiber optic system on these two properties is discussed in Section 3-3.

3-2.3.1 Attenuation. The two main sources of loss in the optical waveguide are scattering and absorption. Typical attenuation loss from a high silica optical fiber without dopants, as a function of wavelength, is shown in Figure 7. The absorption bands which appear at 0.63, 0.73, 0.87, and 0.95  $\mu\text{m}$  result from hydroxyl absorptions in

\*Note: Mention of a product does not indicate endorsement of that product by DNA or Geo-Centers, Inc.

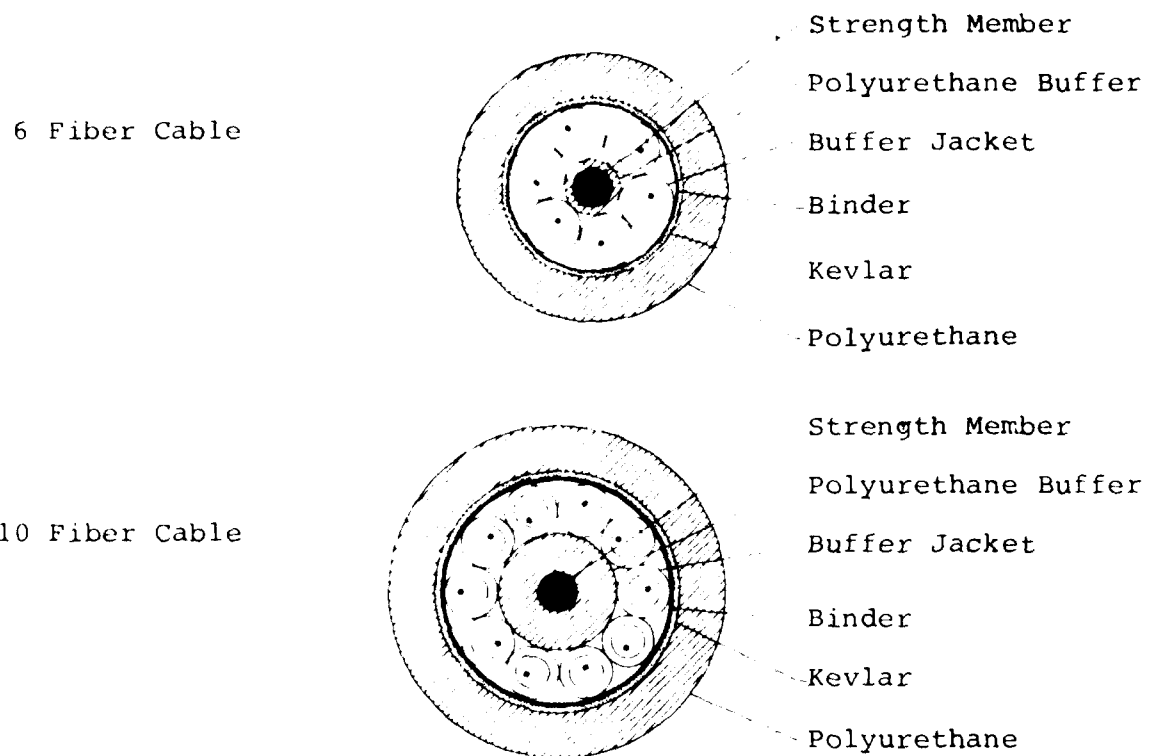


Figure 6. Cross section of SIECOR cable.

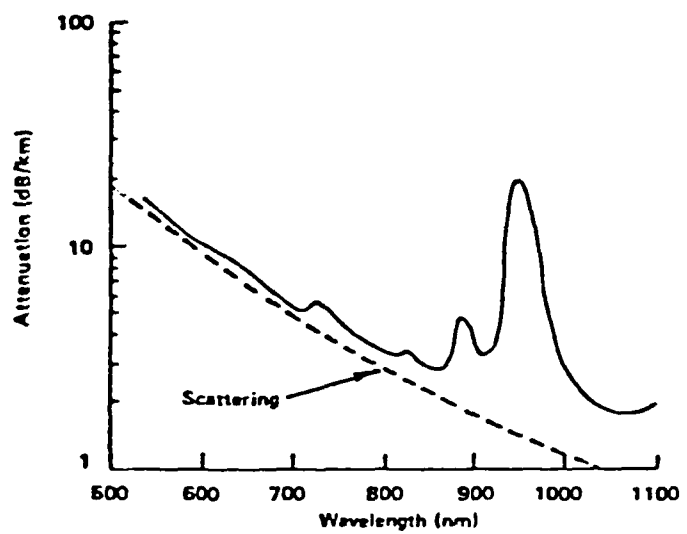


Figure 7. Typical attenuation loss from a high silica optical fiber without dopants.

the glass. Dopants or impurities, if present in the glass, would provide additional absorptions contributing to increased loss. Impurity levels of the order of one part per billion of copper, iron, or chromium, for example, can result in additional loss of one decibel per kilometer (db/km).

Scattering losses in the guide arise from intrinsic material fluctuations. Even in the absence of inclusions or defects which can cause light scattering (and hence loss), the fiber will display an intrinsic scattering caused by density fluctuations, i.e., Rayleigh scattering. These fluctuations in density are thermal in origin and frozen into the bulk glass at high temperature. Of the scattering losses, this probably represents the ultimate lower limit to attenuation (Ref. 9). The dashed curve in Figure 7 shows the intrinsic attenuation contribution from Rayleigh scattering.

Attenuation of optical fibers and cables is customarily expressed in decibels and is normalized to a one kilometer reference length. Thus, from powers transmitted ( $P_t$ ) and received ( $P_r$ ) over a length of  $L$  kilometers:

$$\text{Attenuation} = \frac{-10 \log (P_r/P_t)}{L} \text{ (db/km)} \quad (4)$$

3-2.3.2 Distortion. The bandwidth of optical fibers is limited by a mechanism different from that which limits the bandwidth in a coaxial cable. Attenuation and bandwidth of conventional coaxial cables are closely related because the loss is a function of frequency. This is not true for optical fibers. The characteristics of coaxial cables and optical fibers are compared in Figure 8.

In an optical waveguide, bandwidth is limited by two factors: modal distortion and material dispersion. Modal distortion refers to the broadening of pulses being transmitted through a given fiber caused by different modes arriving at the detector at different

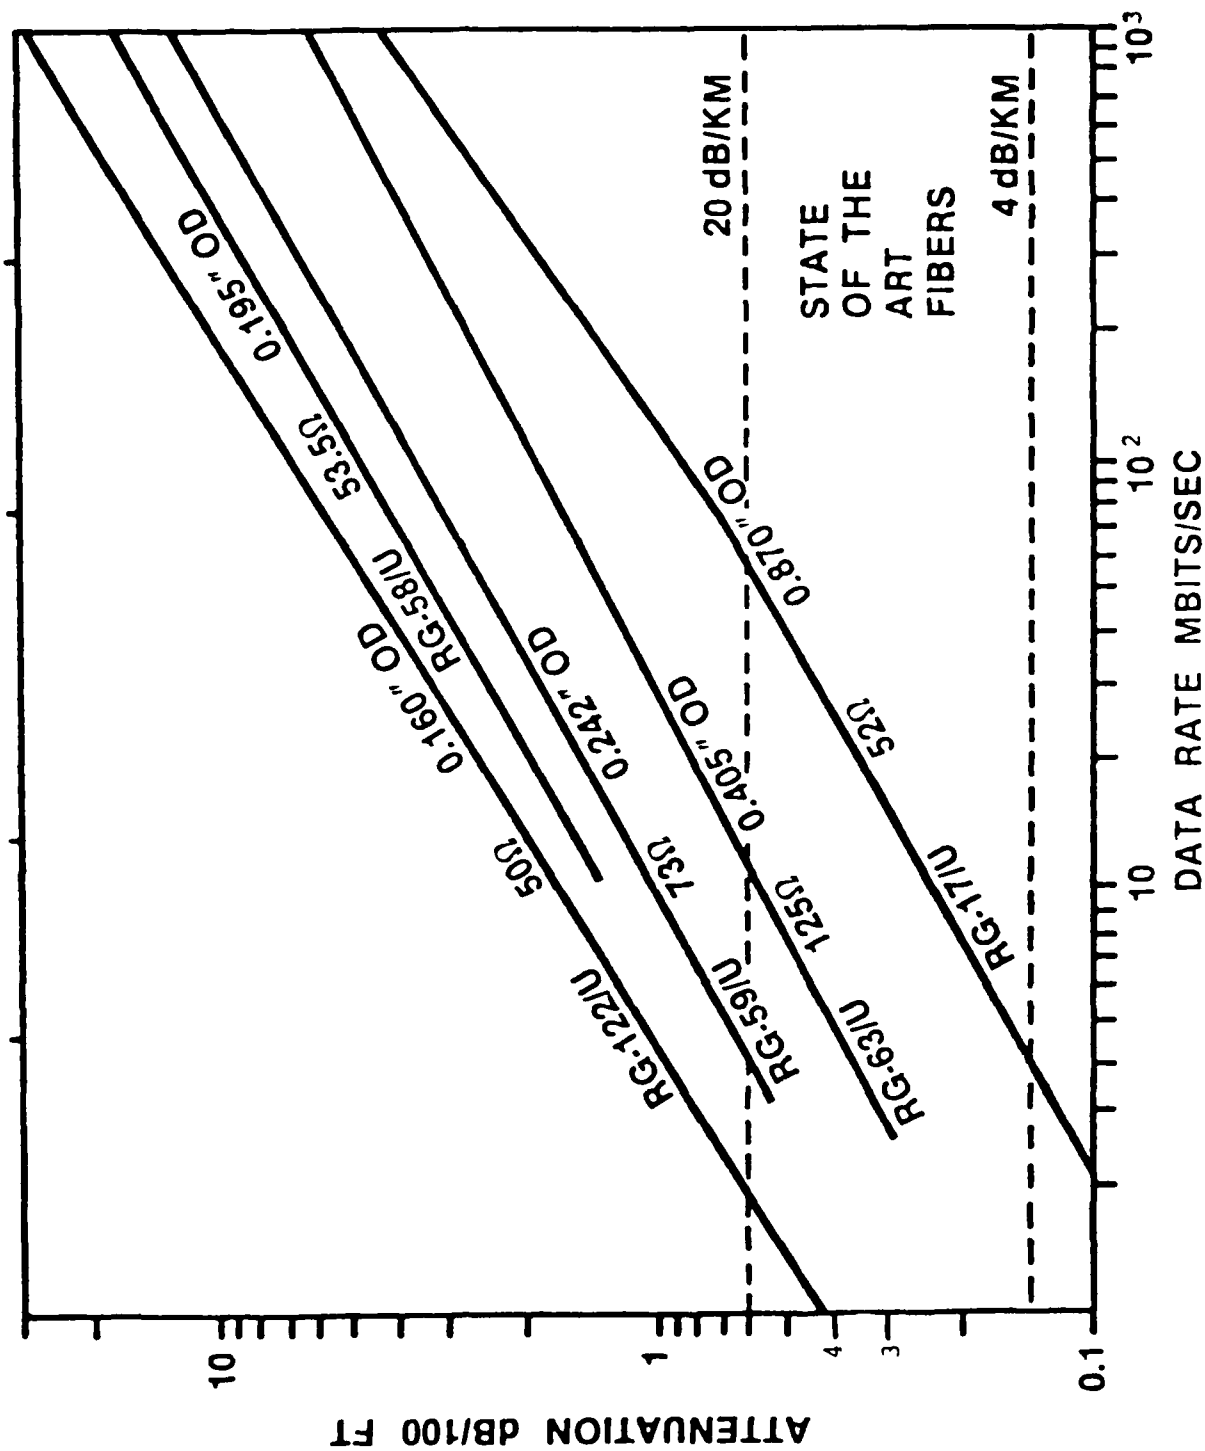


Figure 8. Comparison of coaxial cable and fiber optic attenuation.

times. As mentioned previously, a graded index profile minimizes this limiting factor for a multimode fiber.

Material dispersion is attributable to the wavelength dependence of the refractive index of the material used to form the waveguide. For silica, this dependence has a minimum near 1300 nm. The exact wavelength of the minimum is influenced by the additives and impurities present in the silica core materials. These additives and impurities can give rise to absorption bands which influence the location and absolute value of the intrinsic loss minimum. For a particular application, the significance of the material dispersion depends on the spectral width of the source.

#### 3-2.4 Radiation sensitivity.

The effects of ionizing radiation on optical fiber waveguides are normally subdivided into two broad regimes: transient effects and permanent effects. Transient effects include luminescence and attenuation. Luminescence is most intense in the short wavelength region of the spectrum. Radiation-induced absorption is also generally greatest in this region; thus, the short wavelength component becomes self-absorbed. Appropriate filtering is used to further remove the radiation induced luminescence. The addition of dopants such as Ge, B and P also serves to reduce the luminescence output of the fiber.

Permanent damage due to ionizing radiation and neutrons takes the form of density changes and attenuation. Density changes result in changes in the index of refraction of the glass and may lead to loss of waveguiding in the fibers. Also, the effects of density changes on bandwidth represent a serious, long-term problem for fibers in radiation environments. This results from the sensitivity of the pulse distortion to the index profile of graded index waveguides. Other permanent damage includes changes in the mechanical properties of the fibers.

Table 7 lists the key parameters in the radiation damage of fibers. Results of radiation damage studies can be found in the literature (Ref. 10, 11). Figures 9 and 10 summarize some of the radiation damage results (Ref. 10). Figure 9 shows the total loss sustained in fibers of different composition as a function of gamma ray dose from steady state  $^{60}\text{Co}$  irradiation. The transient response of some of these same fibers to pulsed energetic electrons is illustrated in Figure 10. As can be seen from Figure 10, significant recovery can occur following a dose of transient radiation.

From the figures, therefore, it can be seen that the radiation induced effects can be minimized by proper selection of the fiber material. All of the parameters listed in Table 7 must be considered when selecting a fiber for a specific application. For example, temperature has been shown to significantly influence the recovery of the radiation induced attenuation of the optical fiber waveguide. Table 8, taken from reference 10, lists system requirements and suggests candidate classes of fibers for some applications involving nuclear environments. The actual choice of fiber, will, of course, depend upon the system architecture, attenuation, and bandwidth requirements.

### 3-3 FIBER OPTICS SYSTEMS

Systems employing optical fiber waveguides can be active or passive in nature. Active systems utilize electro-optic converters which take an electrical output from a conventional detector and convert it to an optical analog for transmission over a fiber optic link. This type of system essentially replaces a standard wire link, benefitting from the advantages of fiber cables. The passive system omits the intermediate electrical step and requires a direct radiation to light converter. While fundamentally simpler, passive systems require detector development for many applications. The following systems discussion deals with the active type of system. Passive systems are discussed briefly in the next section.

Table 7. Key parameters in the radiation damage of fibers.

A. Radiation Parameters

1. Total Dose
2. Time After Irradiation
3. Dose Rate
4. Type of Radiation (gamma, neutrons, electrons, etc.)
5. Energy

B. Fiber Parameters

1. Wavelength
2. Temperature
3. Injection Conditions
4. Light Intensity
5. Luminescence
6. Radiation History

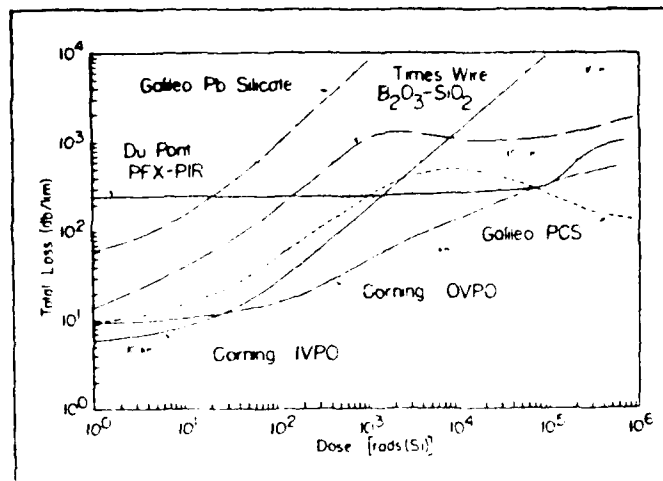


Figure 9 Total loss in optical fiber waveguides as a function of dose during in situ steady state  $^{60}\text{Co}$  irradiation.

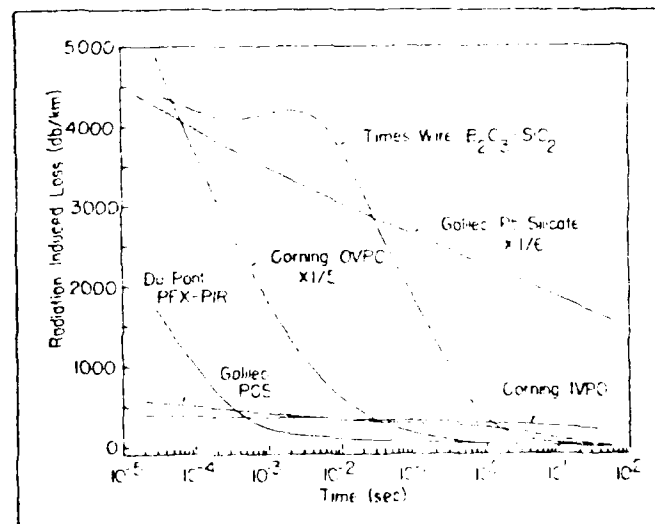


Figure 10 Decay of radiation-induced optical attenuation following a dose of electrons.

Table 8. System requirements, fiber behavior, and candidate fibers for optical communication systems in nuclear environments.

| System Requirements                                                                                           | Fiber Behavior               | Candidates*                                                                                                               |
|---------------------------------------------------------------------------------------------------------------|------------------------------|---------------------------------------------------------------------------------------------------------------------------|
| 1. Minimum downtime                                                                                           | Minimum transient absorption |                                                                                                                           |
| High total dose<br>(unmanned-missile,<br>satellite)                                                           |                              | SiO <sub>2</sub> core<br>(PCS, all glass)                                                                                 |
| Moderate total<br>dose<br>(manned-aircraft,<br>ground links)                                                  |                              | SiO <sub>2</sub> core, Ge-P<br>doped<br>silica core                                                                       |
| 2. Low to moderate<br>dose rate, 1 sec<br>downtime<br>(manned-fallout,<br>reactor environs,<br>space ambient) | Good long term<br>recovery   | SiO <sub>2</sub> core, Ge-<br>doped silica core<br>w/o P,<br>Silicate + Ce,<br>Plastic                                    |
| 3. Neutron flux<br>(weapons, reactor)                                                                         | B-free core &<br>cladding    | SiO <sub>2</sub> core (F-doped<br>silica or polymer<br>clad).<br>binary Ge-doped<br>silica core--SiO <sub>2</sub><br>clad |

\* Choice depends upon system architecture, attenuation and bandwidth requirements.

### 3-3.1 Active System Design.

A block diagram of an optical link is shown in Figure 11. The design considerations of such a link must include distance, information rate (bandwidth), modulation method, and interfacing.

Three factors influence the distance over which a link can propagate information: source power, losses in the fiber and at the coupling points, and the receiver sensitivity. Sources used in most links are either injection diode lasers or incoherent light emitting diodes (LEDs). Table 9 lists several commercially available transmitters along with some useful characteristics. While diode lasers can launch more power into the fiber, LEDs are less expensive and usually more rugged and durable. Also, LED drive circuits are not as complex as those required for lasers.

Table 10 lists several commercially available receivers along with some useful characteristics. Silicon is used almost exclusively for wavelengths less than  $1.0\ \mu\text{m}$ . Current transmitter/receiver research is concentrating on long wavelength ( $> 1.0\ \mu\text{m}$ ) devices. Silicon detectors are not suited for wavelengths longer than  $1.1\ \mu\text{m}$ ; thus, receiver development requires a material suitable for these wavelengths. Compounds of doped gallium arsenide (GaAs) are currently used for receivers and transmitters in this long wavelength region. Table 11 lists some of the source and detector materials available for use.

The incentive for the development of these "second generation" (i.e., long wavelength) fiber optic systems is due in part to the lower optical attenuation of the fibers at approximately  $1.3\ \mu\text{m}$ . Figure 12 illustrates the intrinsic loss of a typical low loss silica fiber used for long wavelength operations (Ref. 12). The loss that is acceptable for a particular application depends on the system design.

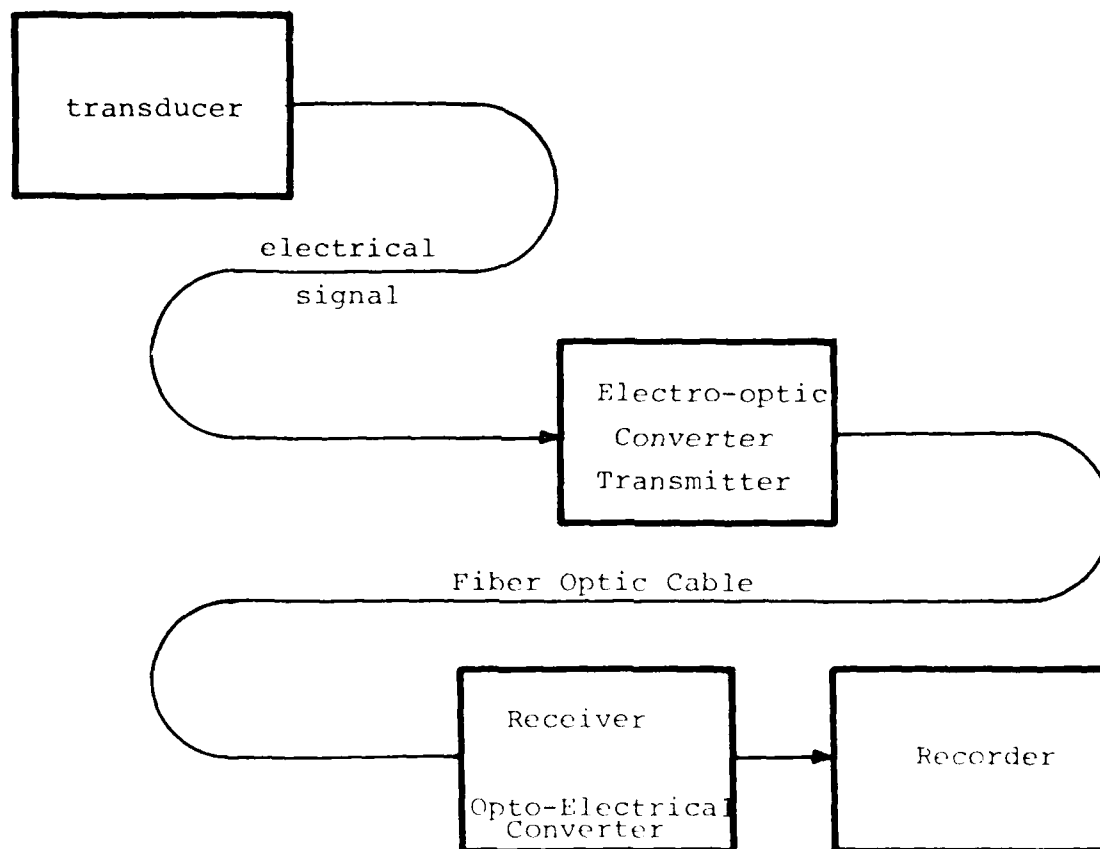


Figure 11. Block diagram of an optical transmission link.

Table 9. Commercially available optical transmitters.

#### ANALOG TRANSMITTERS

| Wave length (s) (μm) | Source Type | Bandwidth (MHz) | Peak Power (mW) | Power Requirements (v & ma) | Rise time (ns) | Manufacturer           | Price (\$) |
|----------------------|-------------|-----------------|-----------------|-----------------------------|----------------|------------------------|------------|
| 660                  | LED         | 3.5             | 35              | ± 12 or 15 ac               |                | Math Associates        | 195.       |
| 850                  | LED         | 8               | 20              | ± 15                        | 50             | Compagnie Lyonnaise    | 1350.      |
| 900                  | GaAs        |                 | 140             | 1.6 & 100                   | 25             | Motorola Semiconductor | 40.        |

#### DIGITAL TRANSMITTERS

| Wave length (s) (μm) | Source Type | Bit Rate (Mb/s) | Peak Power (mW) | Power Requirements (v & ma) | Rise time (ns)  | Manufacturer        | Price (\$) |
|----------------------|-------------|-----------------|-----------------|-----------------------------|-----------------|---------------------|------------|
| 660                  | LED         | 2               | 35              | 7 or 12 ac                  | 150             | Math Associates     | 158.       |
| 820                  | LED         | 2               | 70              | + 5 & 230                   | 25              | Canoga Data Systems | 240.       |
| 840                  | Laser diode | 34              | 1,000           | ± 12 v                      | 1               | Thomson CSF, LTT    |            |
| 850                  | Laser       | .0096           | 100             | 230                         | 10 <sup>6</sup> | Standard Telephone  |            |
| 900                  | LED         | 30              | 20              | 5 & 160                     | 15              | Electro Optic Dev   | 600.       |

Table 10. Commercially available optical receivers.

#### ANALOG RECEIVERS

| Wave length(s) (μm) | Detector type | Bandwidth (MHz) | Power Requirements (v @ ma) | Signal to noise ratio | Linearity | Manufacturer       | Price (\$) |
|---------------------|---------------|-----------------|-----------------------------|-----------------------|-----------|--------------------|------------|
| 600                 | pin           | 3.5             |                             |                       | >1%       | Math Associates    | 235.       |
| 850                 | APD           | 8               | 230 ac                      | 40                    |           | Standard Telephone |            |
| 900                 | APD           | 200             | 15 @ 70                     | 40                    | 3%        | Electro Optic Day  | 1,200.     |
| 905                 | pin           | DC-1            | 12 @ 6                      |                       |           | MERET              | 135.       |

40

#### DIGITAL RECEIVERS

| Wave length(s) (μm) | Detector type | Bit Rate (Mb/s) | Power Requirements (v @ ma) | Bit Error Rate    | Compatability | Manufacturer        | Price (\$) |
|---------------------|---------------|-----------------|-----------------------------|-------------------|---------------|---------------------|------------|
| 660, 890            | pin           | .1              |                             |                   | TTL           | Math Associates     | 100.       |
| 820                 | pin           | 2               | 5 @ 140                     | 10 <sup>-9</sup>  | TTL           | Canoga Data Systems | 240.       |
| 850                 | pin           | 0-2             | + 15                        | 10 <sup>-8</sup>  | TTL           | Compagnie Lyonnaise | 600.       |
| 905                 | pin           | 1               | + 12                        | 10 <sup>-12</sup> | TTL           | MERET               | 370.       |

Table 11. Long wavelength source and detector materials.

Sources

| <u>Type</u>   | <u>Applicable Wavelength</u> |
|---------------|------------------------------|
| GaAlAs        | 0.84 $\mu\text{m}$           |
| AlGaAsSb/GaSb | 1.2 to 1.8 $\mu\text{m}$     |
| InGaAsP/InP   | 1 to 1.6 $\mu\text{m}$       |

Detectors

| <u>Type</u>   |                                | <u>Applicable Wavelength</u> |
|---------------|--------------------------------|------------------------------|
| Si            | PIN                            | Up to 1.1 $\mu\text{m}$      |
|               | APD<br>(Avalanche Photo-Diode) |                              |
| InGaAs        | APD                            | 1 to 1.7 $\mu\text{m}$       |
| Ge            | APD                            | Up to 2.0 $\mu\text{m}$      |
| CdS/CuInSe    | PIN                            | Up to 1.3 $\mu\text{m}$      |
| InGaAsP/InP   | APD                            | 1 to 1.6 $\mu\text{m}$       |
| AlGaAsSb/GaSb | APD                            | 1.2 to 1.8 $\mu\text{m}$     |

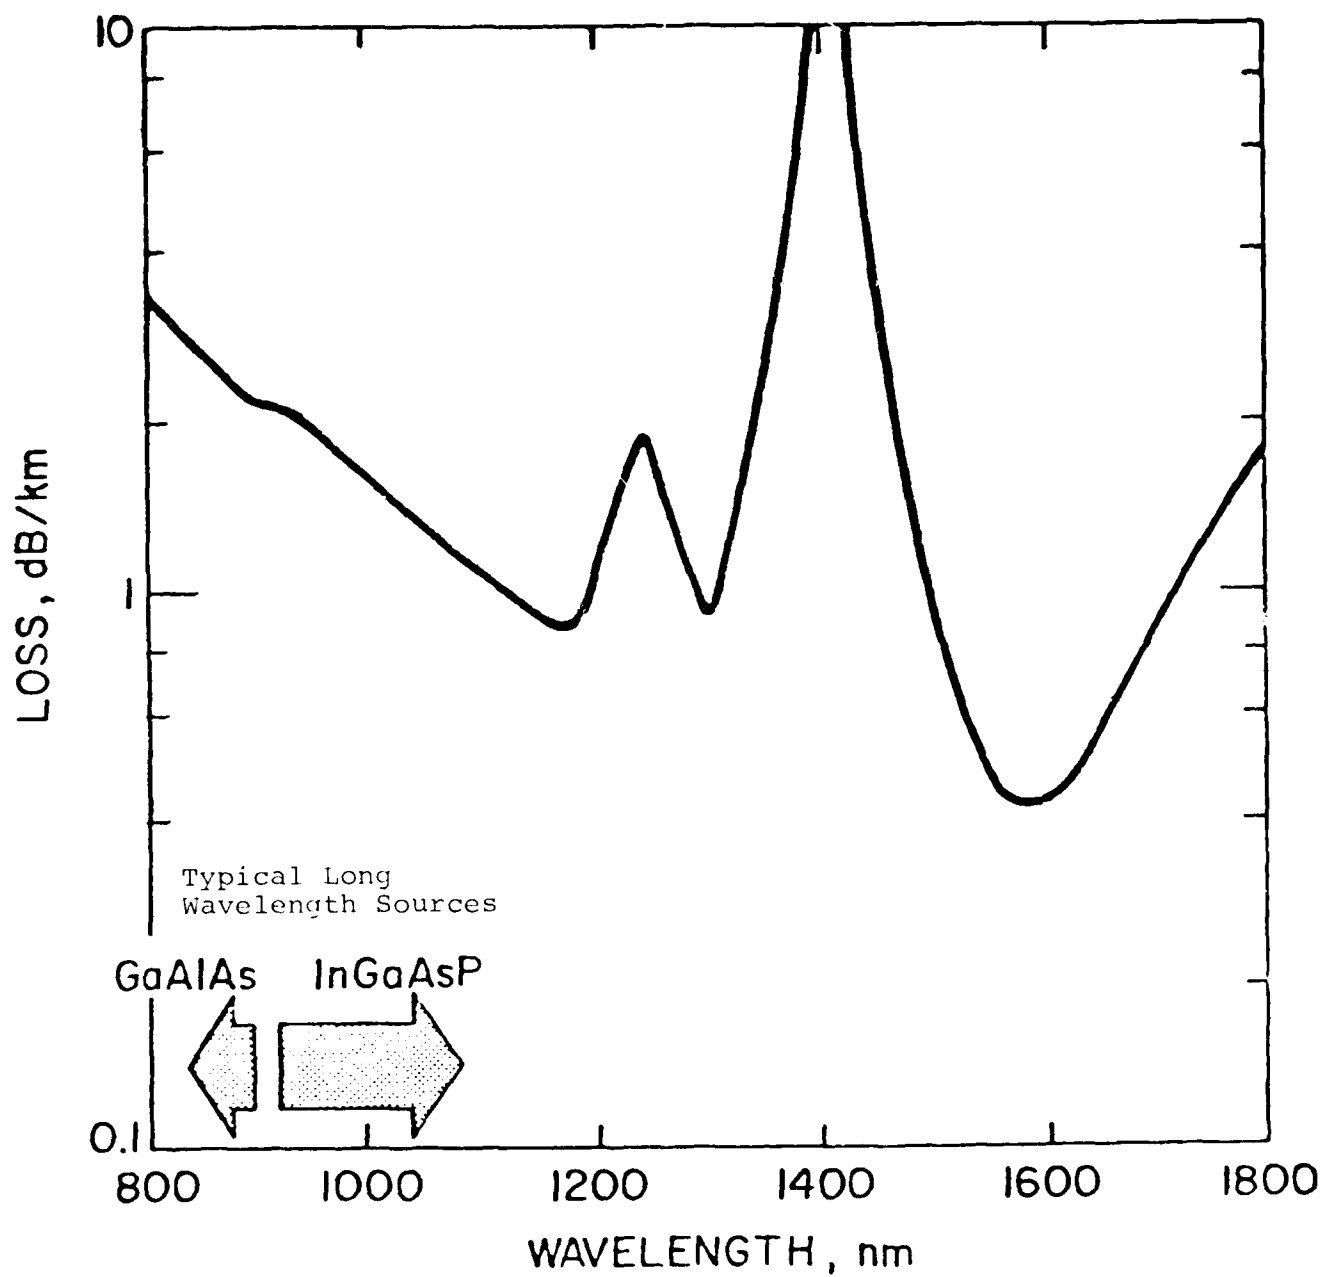


Figure 12. Loss spectra of fibers for long wavelength operation.

The difference between the power level of the transmitter and the required power level at the receiver for a given signal to noise ratio is termed "the budget". The budget is dependent on the bandwidth required. In the case of digital information, this is the bit rate. Budget as a function of bit rate is illustrated in Figure 13. The band termed "digital message" in the figure indicates the range of typical receiver sensitivities; the two upper bands are representative of the ability of the lasers and LEDs to couple power into the fiber. For a given bit rate, the difference, in decibels normalized to 1 milliwatt input power (dBm), between the digital message band and the appropriate source band yields the budget. For example, a LED system operating at 100 Megabits/sec allows for approximately 30 dBm of optical signal attenuation between source and detector. Besides attenuation from the fiber, losses in the connectors and splices, which often dominate the loss terms, also account for the "spending" of the allowed budget.

Optical fiber bandwidth is generally expressed as a bandwidth-distance product. As mentioned previously, bandwidth is limited principally by two factors: modal distortion and material dispersion. Laser systems operating with single mode fibers avoid multi-mode effects, but in the case of LED systems, multi-mode fibers must be used in order to collect enough light from the LED. For good multi-mode fibers, however, the bandwidth distance product caused by residual mode delay differences exceeds 1 GHz-km.

Figure 14 shows the range of bandwidth-distance products for typical InGaAsP LEDs and germanium-doped silica multi-mode fibers having a numerical aperture of 0.2. Also, the bandwidth-distance product for a semiconductor laser, single mode fiber system is shown in the figure. As can be seen, bandwidth-distance products near or exceeding 1 GHz-km can be achieved with systems operating at approximately 1.3 to 1.4  $\mu\text{m}$ .

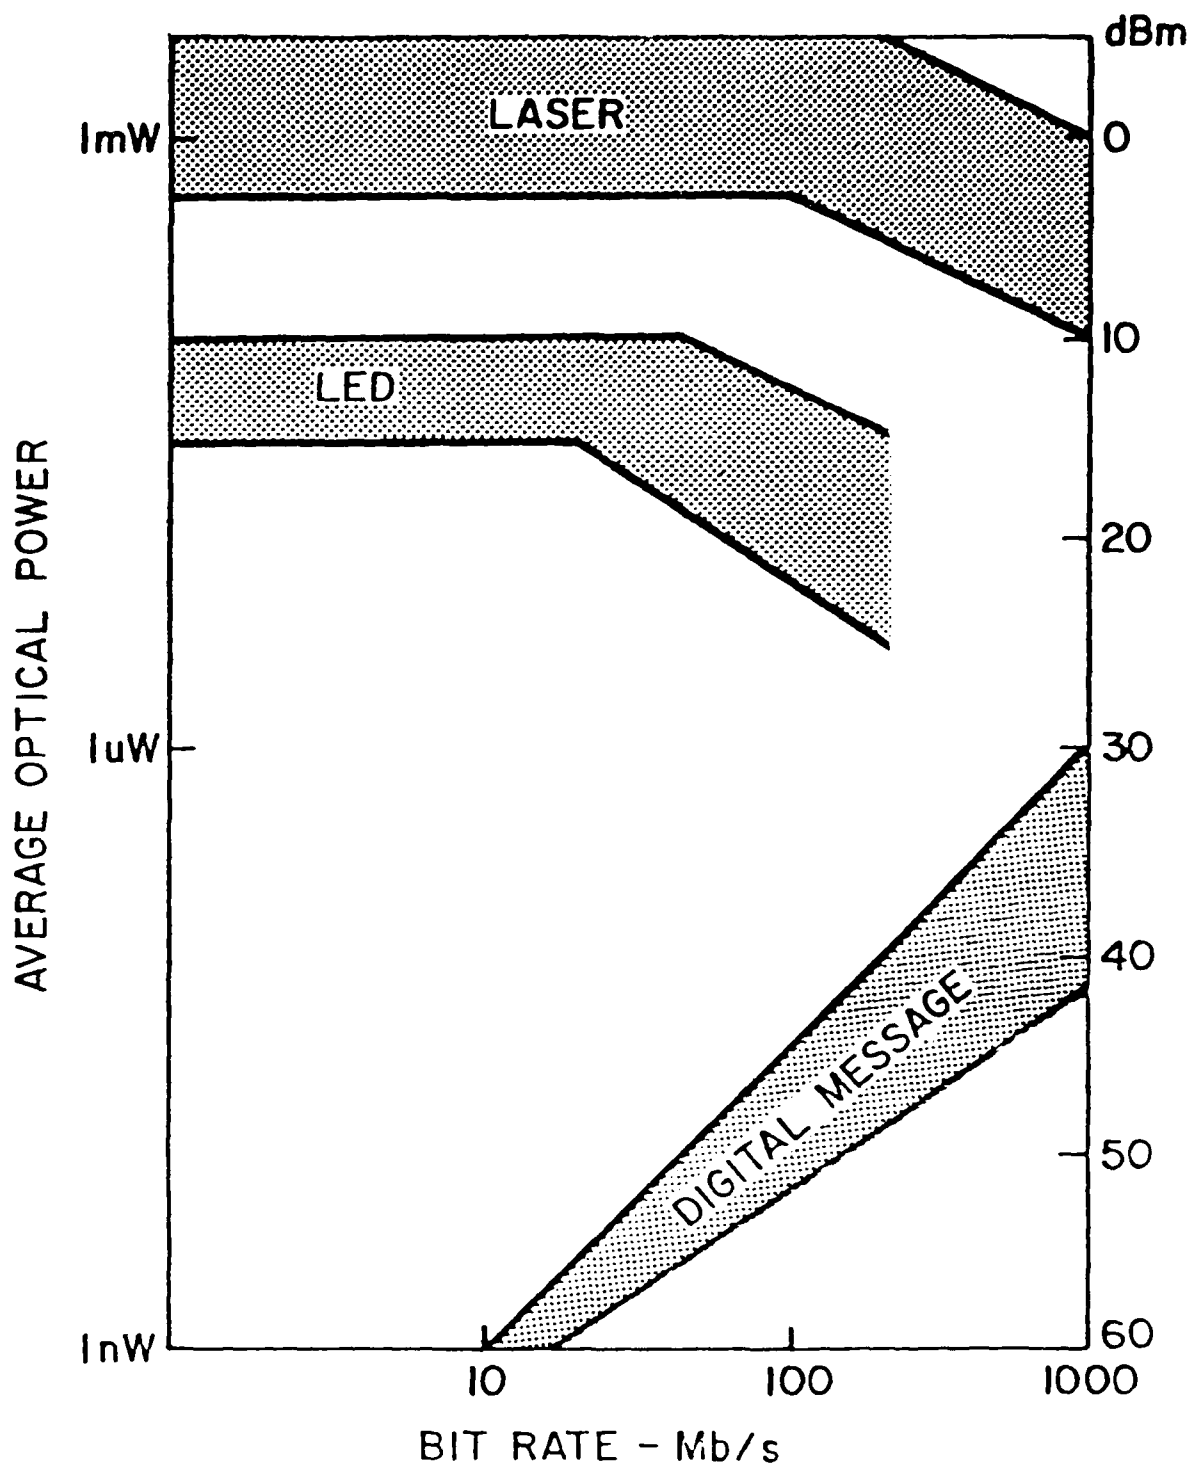


Figure 13. Loss budget for fiber transmission links. (Ref. 12)

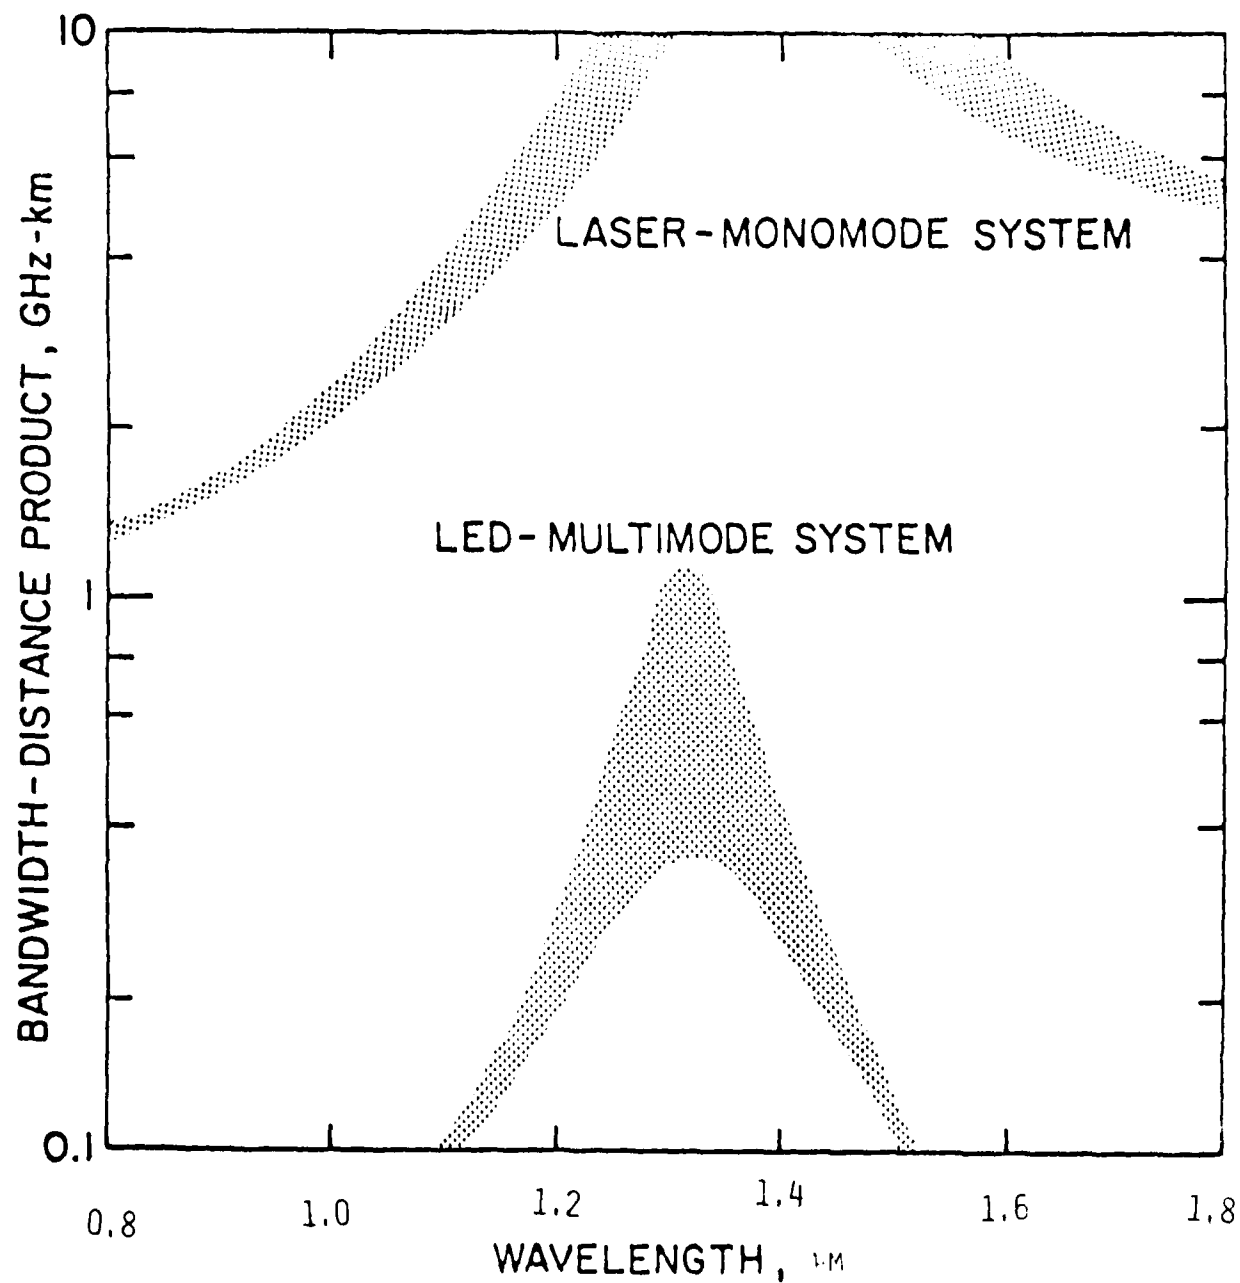


Figure 14. Range of bandwidth-distance products. (Ref. 12)

Modulation of the sources can be either analog or digital. The selection of the modulation method depends upon several factors including the initial format of the information to be transmitted, distance, and desired interface simplicity. With digital modulation, the emitting source is driven to one of only a few discrete levels (usually 2) and the information to be transmitted is coded.

## SECTION 4

### USE OF FIBERS IN UGT

The cabling requirements for an underground nuclear test have been briefly described. Considerable engineering development has gone into solving the cabling problems which complicate the fielding of remotely monitored measurements. For example, in order to avoid zero-time noise and subsequent loss of data, a large effort has been expended on the proper grounding and shielding of the cable runs.

The advantages of fiber optics, as discussed in Section 3, have been utilized in underground nuclear testing. In this application, the bandwidth, freedom from EMI, low cost, and lightweight can all be of significant advantage. Since 1977, UGT experiments utilizing fiber optics have been fielded at the NTS (Ref. 13). Early applications involved experiments for characterizing fibers in the UGT environment. The success of these early measurements has developed confidence in fibers to the point of fielding non-redundant fiber optic links taking full advantage of their useful characteristics. The advantages of fibers as applied to UGT are discussed in this section, and some of the work involving fiber optics at the NTS is reviewed.

#### 4-1. ADVANTAGES OF FIBERS FOR UGT.

Several advantages can be realized by utilizing fiber optics in UGT applications. Table 12 compares the 3 dB frequency response, procurement costs, and weights for one kilometer lengths of SIECOR cable and a high quality coax cable. As mentioned in Section 3, the SIECOR cable is a six or ten fiber bundle. The large bandwidth of optical fibers presents a major advantage for this type of transmission

Table 12. Comparison of high quality coax cable and SIECOR optical fiber cable.

|                | Bandpass | Procurement Cost     | Weight |
|----------------|----------|----------------------|--------|
| RG 331         | 1.3 MHz  | \$1840.00            | 220 kg |
| SIECOR 6 fiber | 200 MHz  | \$1400.00* per fiber | 46 kg  |
| 10 fiber       | 200 MHz  | \$1230.00 per fiber  | 66 kg  |

\*Cost comparisons to coax should include cost of transmitter and receiver (see text).

link over a conventional metallic cable. Comparing the optical fiber bandwidth with the typical UGT measurement requirements (Table 3) illustrates that the capability of the fiber is severely underutilized if each measurement channel is transmitted on its own fiber. The advantage of the fiber is the enhanced multiplexing capabilities it affords the user. Transmitting multiple data channels along the same transmission line provides cost savings (both procurement and installation), installation time savings, and helps simplify the grounding and shielding effort.

Cost comparisons between fiber optic and coaxial cable links should include the cost of the transmitter and receiver required for the fiber link. If the multiplexing capabilities afforded by the fiber cable are not taken advantage of, (i.e., direct channel for channel replacement of the coax cable), each fiber channel will require a transmitter and receiver. Referring to Table 9, the current costs (1980) of representative transmitters range from approximately \$200 to \$500; from Table 10, receiver costs range from approximately \$100 to \$600. (It should be noted that current fiber and component costs are decreasing.) From these examples and the procurement cost comparison given in Table 13, it is seen that even with a direct channel for channel replacement of high quality coax links with fibers, the fiber links are procurement cost competitive.

For the total cost picture, installation costs must be considered. The bulky coaxial cables incur handling costs approximately equal to their procurement costs (Ref. 13). The lightweight fiber cables, where several channels are installed per cable, reduce these costs significantly. Cable savings provided by the enhanced multiplexing capabilities assures an even greater cost benefit with fiber links. For example, a system designed for an upcoming event replaces up to 92 twisted, shielded pair links with a single fiber bundle (Ref. 18).

Another advantage of fibers lies in the fact that all-dielectric data transmission links become possible with fiber optic cables. Any reduction in the ground plane available for EMI induced noise propagation goes a long way in simplifying the grounding and shielding requirements. Resultant decreases in or elimination of zero-time noise allow much more reliable data recovery in the micro-second time regime. Also, the non-metallic cables help minimize signal coupling between experiments, i.e., cross-talk.

Many of the disadvantages anticipated with the use of fiber optic cables did not materialize during field use. As discussed in the next section, the fiber cables have proven to be surprisingly rugged in field applications, and current engineering developments have yielded splice losses in cables of less than 1 dB/km (Ref. 14). Cable requirements unique to underground nuclear tests have been met with minimal compromise of the optical and mechanical properties of the fibers.

#### 4-2. DIAGNOSTIC APPLICATIONS.

In addition to DNA, the Department of Energy (DOE) also sponsors underground nuclear tests. Many of the experiments fielded in support of a DOE-sponsored event are of the diagnostic type. These tests are usually conducted at the bottom of deep holes rather than in tunnels as is typical of most DNA-sponsored events (Ref. 15). Hole depths vary from 200 to 1000 meters; hole diameters range from 90 to 225 cm. A cylindrical steel rack, up to 70 meters long, houses the nuclear device and the experiments which are mounted at distances varying from 50 cm to the length of the rack from the device.

The operation of lowering the rack to the bottom of the hole and the procedure followed to fill and plug the hole require that the cables connecting the experiments with the recorders located uphole withstand severe mechanical stresses. Since the hole is

completely filled with layers of sand, gravel, and epoxy, the cables are exposed to these materials over long distances. A schematic of a typical rack geometry (for a DOE event) is shown in Figure 15.

The first application of fiber optics to UGT examined the feasibility of fiber optics use in the NTS environment (Ref. 13). For this first test, tools and capabilities had to be developed. Radiation induced luminescence and absorption were measured for two types of exposed fibers. These data were then transmitted to recording stations along 700 meters of continuous CORGUIDE cable. A passive fiber optic system was thus formed.

Gas blocking of the CORGUIDE cable was accomplished by compressing a 10 cm length of cable in a specially shaped block under increased temperature and pressure. All leak paths, except the strength member, were thus sealed. The outer jacket of the cable was scraped away just outside the block and this area was potted with epoxy which wicked into the stranded Kevlar. After perfection, a gas block, field installed using this technique, resulted in optical losses less than 0.2 dB.

The results of the first field test provided radiation effects data for fibers and demonstrated the feasibility of using fiber optic cables for data transmission in the UGT environment. Subsequent work utilizing fiber optics systems for UGT diagnostics has incorporated radiation to light converters for gamma and neutron detection (Ref. 16).

In one system, a Cerenkov converter was used to detect gamma rays. A fused silica converter, actually a PCS fiber, was used for the transducer. The data were transmitted to the recording stations over fiber cables. Filters were used to limit material dispersion by narrowing the optical bandpass to 1 or 2 nm around the 800 nm wavelength chosen for data transmission. The system was then able

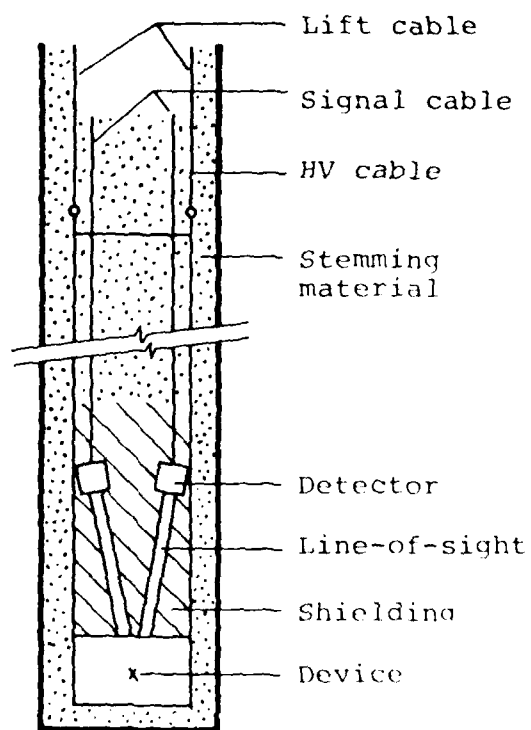


Figure 15. Schematic of a typical NTS rack geometry.

to approach a 1 GHz bandwidth.

A second system that has been successfully fielded provides space and time resolved neutron imaging. The signals from liquid scintillators, arranged in a close packed array, are transmitted along fiber cables to uphole recording stations. Six meters of PCS fiber, which has good radiation resistance but relatively poor bandwidth capability, connected the detector array to the graded index fiber transmission line. This helped limit the radiation induced transient response while still providing the required bandwidth.

Fiber cables from three vendors were utilized. All vendors provided gas tight cables able to pass the gas block requirements. Strength members incorporated into the cable were non-metallic providing an all-dielectric transmission link. In both the gamma and neutron system, the fiber cables proved to be surprisingly rugged with no special handling required. In several instances, the uphole portion of the cable has been retrieved without any measurable degradation in any property.

#### 4-3. EFFECTS MEASUREMENT APPLICATIONS.

In Section 2, examples of effects measurements taken during an underground test were given. Transducers currently used in this application require bias voltage and provide electrical signals representing the parameter of interest. Without extensive transducer development, then, these systems lend themselves more readily to the use of active fiber optic links. All of the advantages of the fiber optic cables are still realized (e.g., cost, EMI immunity, etc.). The results of an application of a fiber optics link to a strain gauge channel fielded during a DNA sponsored underground test are given in this section.

Strain is mathematically defined as the change in length divided by the original length. Since even the most rigorous and

complex analytical methods of determining strain in a loaded body are only approximate, measurements under realistic loading conditions are necessary for an optimum mechanical design of a system. Strain gauge data have, at times, been incomprehensible due to failures and grounding and shielding problems. Great care must be exercised when fielding strain gauges if noise-free, usable, signals are to be recorded.

Several types of strain gauges are fielded during a typical UGT. The principle of operation for wire and foil gauges involves the change in resistivity that accompanies dimensional changes in conductors. In a typical wire strain gauge, a wire about 10-12 cm in length and 0.0025 cm in diameter is formed into a grid shape and bonded to the surface to be tested. Foil gauges are made by printing the desired pattern on a thin sheet of metal alloy foil with an acid-resistant ink, then etching away the imprinted portion. Any strain in the surface will be transmitted to the conductor, with a corresponding change in resistance producing a measurable output. The change in resistivity is usually measured by placing the gauge in a bridge configuration as shown in Figure 16.

For the first test of fiber optics in this application, a fiber link from the instrumentation alcove to an underground recording shack was run in parallel to a coaxial cable link (Ref. 17). The data from the foil strain gauges were transmitted along both links. Standard FM multiplex techniques were utilized in the instrumentation alcove. LEDs and PIN diodes were chosen for the transmitter/receiver combination. The specifications of the fiber optics link included: bandwidth-8MHz, dynamic range-40 dB.

Data transmitted on the coaxial cable link from one of the foil strain gauges are shown in Figure 17. The two large "spikes" occurring prior to 400 microseconds are caused by cable plant ringing and make it impossible to recover data for early times. Data transmitted on the fiber link are shown in Figure 18. As can be seen, the

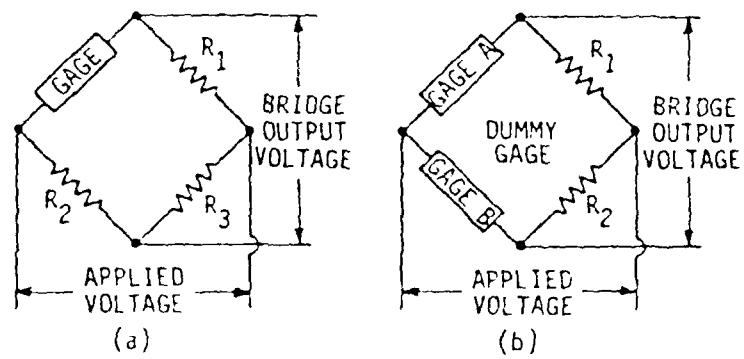


Figure 16. Typical strain gauge bridge configurations.

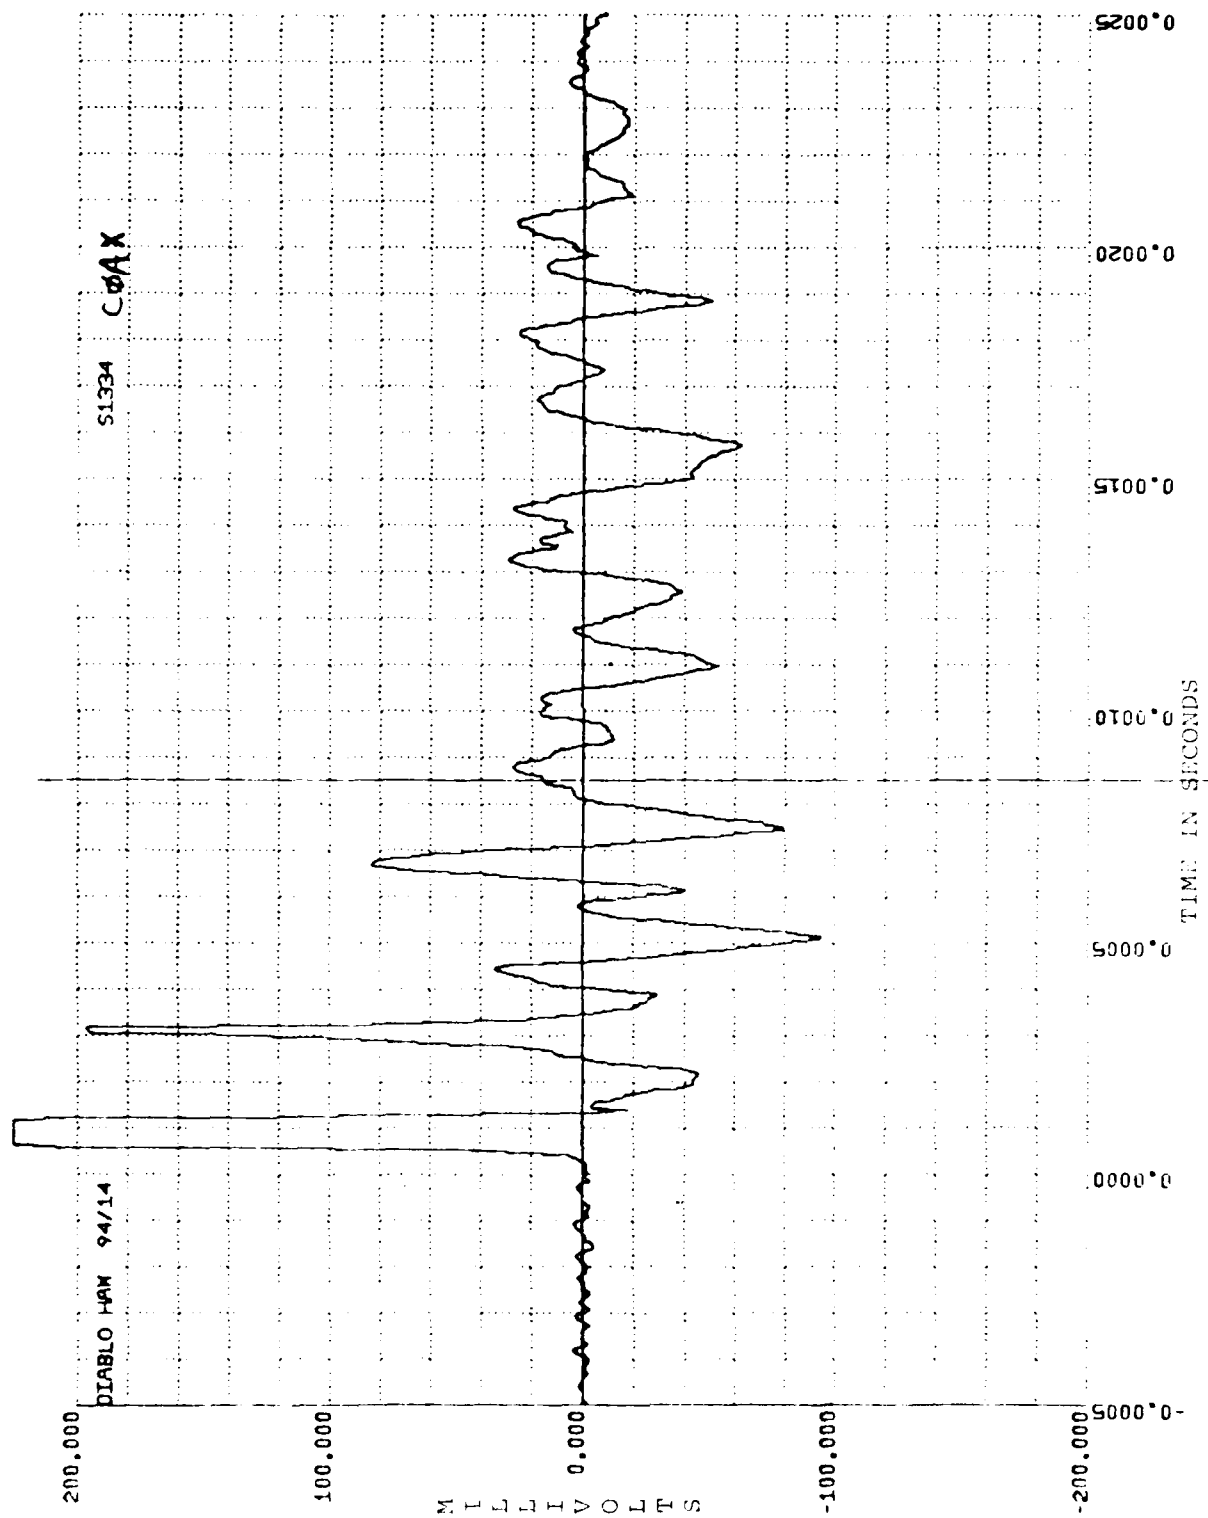


Figure 17. Strain gauge data transmitted on coaxial cable.

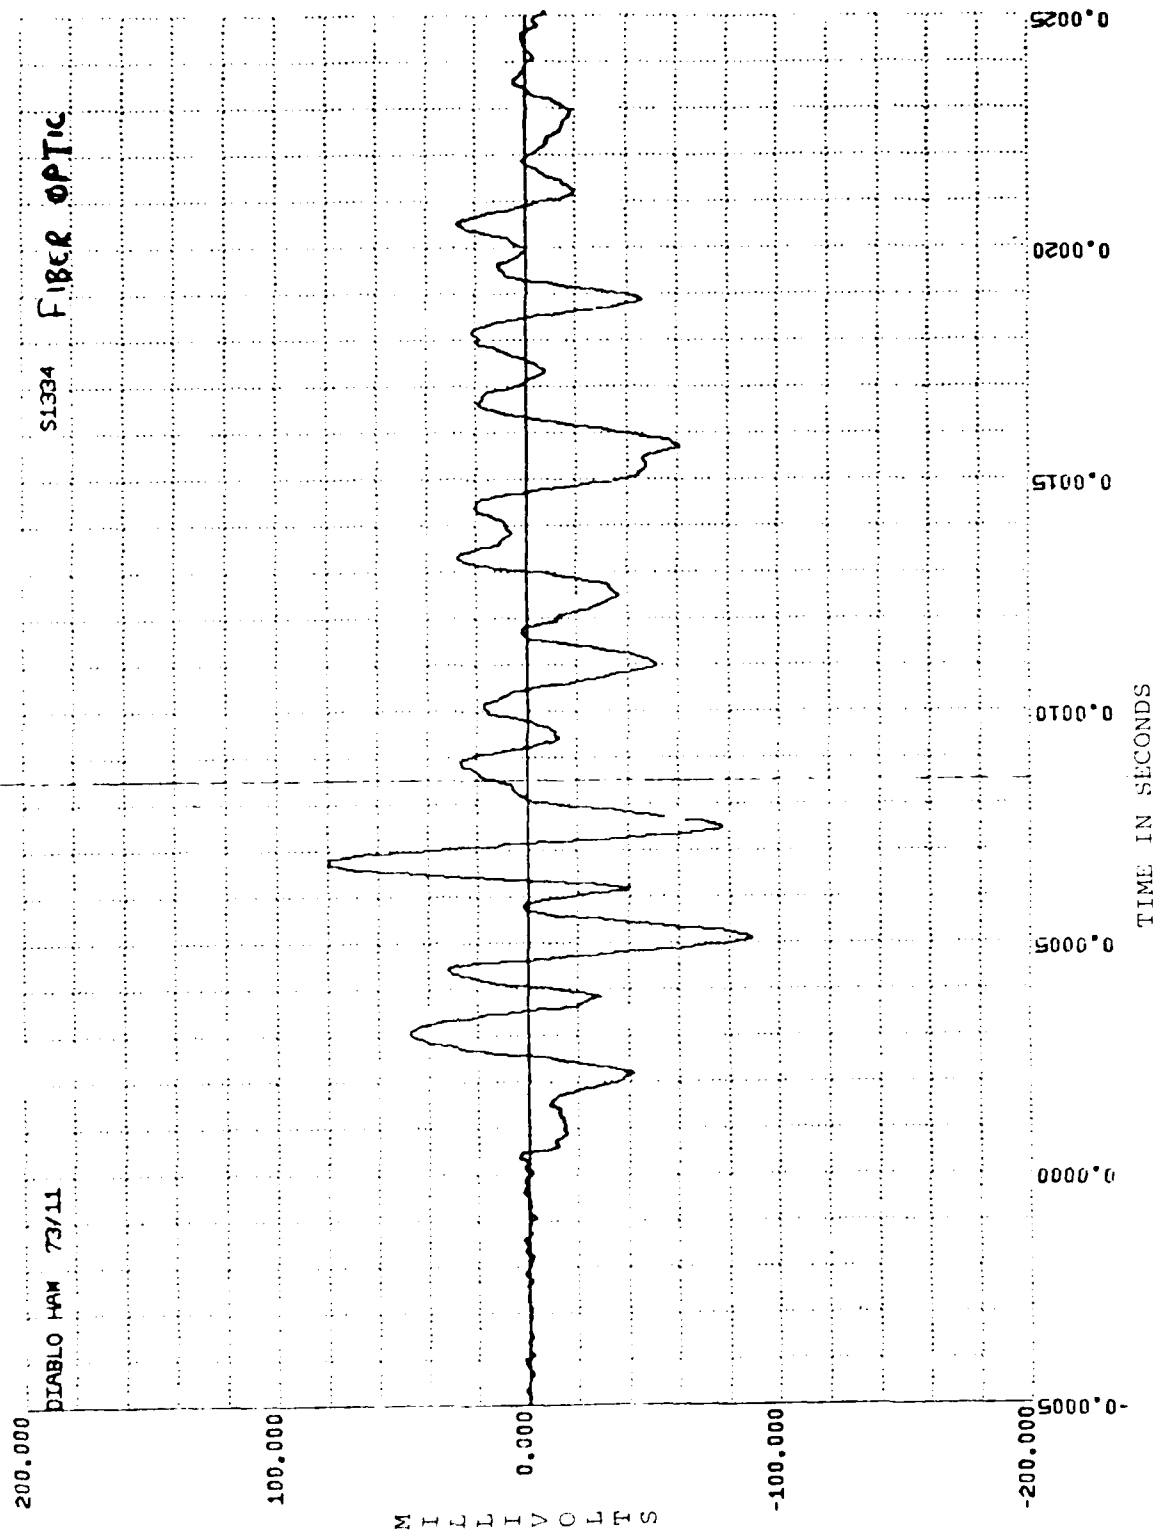


Figure 18. Strain gauge data transmitted on fiber optic cable.

dielectric link eliminated the early time noise and, therefore, provided strain gauge data for times less than 400 microseconds. These results exceeded expectations in terms of noise spike suppression and signal-to-noise ratio.

#### 4-4. FUTURE USES OF FIBERS IN UGT.

Data transmission links utilizing fiber optics are planned for upcoming DNA-sponsored events. The results of previous work, as discussed in this report, have been very encouraging. The redundant, parallel coaxial cable transmission link will be eliminated in future events (Ref. 17). Multiplexed, digital fiber optics links have been designed and are ready for field use (Ref. 18). Current work is underway towards development of transducers which yield optical signals directly (Ref. 19). Also, fiber characterization studies in the UGT environment are continuing (Ref. 20).

## SECTION 5

### CONCLUSIONS AND RECOMMENDATIONS

Fiber optics can and have been used to great advantage in underground nuclear tests. The interest in fiber optics is justified by numerous advantages over metallic conductors including:

- . lower costs
- . elimination of cable plant ringing
- . increased bandwidth
- . elimination of cross talk between experiments

Experience with fiber cables at NTS indicates that their performance exceeds expectations in terms of ruggedness. Results of tests show minimal fiber degradation during and after the rough handling typical of the NTS environment.

Fiber optic research is continually undertaken in the civilian market, particularly in the communications field. While much of this work leads to results useful in all applications, the unique requirements and environment of underground nuclear tests require specialized research and development in order to capitalize on the advantages of fiber optics. In particular, the following areas should be investigated:

- 1) Economic and technical study to evaluate replacement of the permanent cable runs with fiber optic transmission links. The study should include evaluation of transmitters, receivers, and possible multiplexing techniques. Multiplexing possibilities are greatly enhanced due to the much greater bandwidth capabilities of optical fiber transmission systems.

- 2) Specifications and designs of optical links for standard gauge types: strain, impulse, etc.
- 3) Development of mechano-optical transducers as applicable to parameters of interest to DNA. This effort should include the application of LASL's diagnostic work with fibers to DNA events. Also, current transducer development work at the Naval Research Laboratory should be evaluated for possible DNA UGT applications.
- 4) Evaluation of fiber optic use for data transmission from gauge to instrumentation alcove. These studies would have to consider radiation hardening of transmitters. The advantage is in the reduction of zero time noise.
- 5) Fiber effects studies to provide radiation behavior data where data do not presently exist. Due to the non-linear behavior of fiber when exposed to nuclear radiation, it is extremely difficult and risky to extrapolate existing data to radiation fields of interest. In addition, consideration should be given to the possibility of utilizing photo-bleaching for annealing radiation-induced effects.

In addition to benefitting UGT, advances in fiber optic technology can greatly impact other DNA activities such as hardening of military components and simulation and testing in high radiation fields. Using the UGT environment as a test bed, optical fibers can be characterized in severe radiation and stress environments. Due to the importance of these characteristics and the potential benefits, it is recommended that DNA take a lead role in the research and development of fiber optic technology for use in adverse test and simulation environments.

## SECTION 6

### REFERENCES

1. Technical Directors Handbook, Defense Nuclear Agency, Field Command, Kirtland AFB, Albuquerque, New Mexico (1977).
2. Leu, Vernon (EG&G), private communication, April 1980.
3. DNA Cable Status Board, November 1979.
4. Scott, L., and Parkinson, R., "Grounding and Shielding Requirements for the Radiation and EMP Environments of an Underground Nuclear Test," SAI report SAI77-015-CS, March 1978.
5. Kitchen, W. R., Naumann, W. J., and Vollmer, D. W., "Fast Recovery Strain Measurements in a Nuclear Test Environment," UCRL-81771, April 1979.
6. Montrerth, M. R., "Optical Fiber Drawing Techniques," Optical Spectra, October 1978, pages 42-47.
7. Jaeger, R. E., "Optical Communication Fiber Fabrication," present at the Electro Optics/Laser '76 Conference, New York, N.Y., September 1976.
8. SIECOR Optical Cables, Inc. Technical Bulletin.
9. Keck, D. B., and Tynes, A. R., "Spectral Response of Low-Loss Optical Waveguides," Applied Optics, 11 7, July 1972.
10. Friebele, E. J., "Optical Fiber Waveguides in Radiation Environments," Optical Engineering, 18, 6, November-December 1979. (Contains a bibliography of the important literature on the effects of ionizing radiation on fiber optic waveguides).
11. Webb, R. C., Isaacson, L., Marram, E. P., "Response of Fiber Optic Waveguides to Ionizing Radiation," Optical Engineering, 18, 6, November-December 1979. (Contains a bibliography of the important literature on the effects of ionizing radiation of fiber optic waveguides).
12. Gloge, D., "Second Generation Fiber Systems," Optical Spectra, November 1979, pages 50-52.

13. Lyons, P. B., et al, "Fiber-optic Utilization at the Nevada Test Site," LASL Report No. LA-UR-77-2201, November 1978.
14. Lyons, P. B., "Fiber-optic Technology Review," LASL Report No. LA-UR-80-607, March 1980.
15. Wolff, W. P., "A Typical LASL Underground Nuclear Test," LASL Mini-Review 77-2, Los Alamos Scientific Laboratory, June 1977.
16. Lyons, P. B., et al, "Fiber-optic Applications in Nuclear Testing," LASL Report No. LA-UR-79-2825, October 1979.
17. McNairy, R., Honey, F., (LASL, WX-10), private communication, February 1980.
18. Naumann, W. J., Hogg, R. D., "A Multiplexed Fiber Optic Link for 5 to 20 KHz Data in Nuclear Field Tests," presented at the DNA Symposium on Fiber Optics in the Nuclear Environment, March 1980.
19. Orrell, S., "Mechano-Optical Transducer Development," EG&G, Inc., DOE Contract No. DE-AC08-76NV01183, December 1979.
20. Heckman, R. C., Allen, J. W., Duce, S. R., Hohlfelder, J. J., Machin, E. D., "Miners Iron Test of Optical Fibers," presented at the DNA Symposium on Fiber Optics in the Nuclear Environment, March 1980.

# DISTRIBUTION

1. The distribution of the population is as follows:

2. The distribution of the population is as follows:

3. The distribution of the population is as follows:

4. The distribution of the population is as follows:

5. The distribution of the population is as follows:

6. The distribution of the population is as follows:

7. The distribution of the population is as follows:

8. The distribution of the population is as follows:

9. The distribution of the population is as follows:

10. The distribution of the population is as follows:

11. The distribution of the population is as follows:

12. The distribution of the population is as follows:

13. The distribution of the population is as follows:

14. The distribution of the population is as follows:

15. The distribution of the population is as follows:

16. The distribution of the population is as follows:

17. The distribution of the population is as follows:

18. The distribution of the population is as follows:

19. The distribution of the population is as follows:

20. The distribution of the population is as follows:



# DEPARTMENT OF THE AIR FORCE (Continued)

Headquarters Space Division  
Air Force Systems Command  
ATTN: SKY, C. Kennedy  
ATTN: YCD, R. Spray  
ATTN: YCD, R. Staubs  
ATTN: YCD, F. Brininstool  
ATTN: YCPT, D. Bartel  
ATTN: YN, J. Sweeney  
ATTN: YN, A. Varisco  
ATTN: YNV, J. Turnipseed  
ATTN: YN, B. Brady

Rome Air Development Center  
Air Force Systems Command  
ATTN: ESR, A. Yang  
Copy ATTN: ESR, A. Wall

Strategic Air Command  
Department of the Air Force  
ATTN: E. Winger

## DEPARTMENT OF ENERGY

Department of Energy  
Albuquerque Operations Office  
ATTN: TIII

## AT&T GOVERNMENT AGENCY

Institute for Telecommunications Sciences  
ATTN: J. Ball

## DEPARTMENT OF THE ARMY (Continued)

Ames Research National Laboratory  
ATTN: J. Levy

ARPA, Inc.  
ATTN: W. Rosenblatt

Lawrence Livermore National Lab  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Los Alamos National Laboratory  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Naval Air Station, Jacksonville  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Naval Air Station, Jacksonville  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

# DEPARTMENT OF DEFENSE CONTRACTORS

Acurex Corporation  
ATTN: E. Treibes

Advanced Research & Applications Corp.  
ATTN: R. Armistead

Aerospace Corporation  
ATTN: W. Biecker  
ATTN: W. Bower  
ATTN: W. Hsueh

AT&T  
ATTN: J. Maruch

University of Arizona  
ATTN: J. Burke

Artec Associates, Inc.  
ATTN: D. Baum

Automation Industries, Inc.  
ATTN: D. Moltis

BPM Corporation  
ATTN: J. Neighbors

Bell Telephone Labs  
ATTN: J. Fleming

Bell Telephone Labs  
ATTN: J. Caldwell  
ATTN: M. G. H. Kennedy  
ATTN: J. M. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Boeing Company  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.  
ATTN: J. J. J. J. J.

Boeing Company, Inc.  
ATTN: J. J. J. J. J.

# DEPARTMENT OF DEFENSE CONTRACTORS (continued)

## Electro-Optics, Inc.

ATTN: J. H. Smith  
ATTN: W. H. Smith

## Electro, Inc.

ATTN: R. Lynn  
ATTN: M. Nelson  
ATTN: J. Davies

## Electro, Inc.

ATTN: J. J. Javanaro  
ATTN: J. J. J. J. J.

## Electro, Inc.

Electro Engineering, Inc.  
University of New Mexico  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical Corporation

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro-Optical Corporation

ATTN: J. J. J. J.

## Electro-Optical Corporation

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro, Inc.

ATTN: J. J. J. J.

# DEPARTMENT OF DEFENSE CONTRACTORS (continued)

## Electro-Optical Products Division

ATTN: M. M. M.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: A. A. A.

## Electro, Inc.

ATTN: J. J. J. J.

## Electro-Optical Laboratory

ATTN: J. J. J. J.

## Electro-Optical

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical Corporation

ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

## Electro-Optical, Inc.

ATTN: J. J. J. J.  
ATTN: J. J. J. J.

DEPARTMENT OF DEFENSE CONTRACTORS (continued)

Mitre Corp.  
ATTN: B. Metcalf  
ATTN: C. Parato

Nichols Research Corp., Inc.  
ATTN: N. Chen

Northrop Corp.  
ATTN: L. Scola  
ATTN: A. Saliba

Northrup Research Corp.  
ATTN: R. Doyle

Physics Applications, Inc.  
ATTN: T. Vincent

Systems International, Inc.  
ATTN: J. Luchman  
ATTN: Technical Library

Solytechnic Institute of New York  
ATTN: A. Gilmer

SRI Associates  
ATTN: W. Graham  
ATTN: J. Gorman  
ATTN: J. Kras

Stowell International Corp.  
ATTN: D. Taylor  
ATTN: A. DeGamber  
ATTN: J. Smith

University of Rutgers  
ATTN: J. Smith

Technica Applications, Inc.  
ATTN: J. Miller

Technica Applications, Inc.  
ATTN: Technical Library

Technica Applications, Inc.  
ATTN: W. Mendes  
ATTN: J. DeGamber

Technica Applications, Inc.  
ATTN: W. Mendes

Technica Applications, Inc.  
ATTN: J. Smith

DEPARTMENT OF DEFENSE CONTRACTORS (continued)

Northwestern Institute of Technology  
ATTN: R. Watson

Radco, Inc.  
ATTN: L. Stewart

Recon, Inc.  
ATTN: J. F. W. Davis

RI International  
ATTN: A. Abrahamson  
ATTN: S. Lee  
ATTN: L. Feough

Stamata Systems Group  
ATTN: L. Walmsley

Systems Science & Software, Inc.  
ATTN: J. Grine  
ATTN: P. Coleman

Teletype Brown Engineering  
ATTN: B. Henderson  
ATTN: G. Lindwehr

Tetra Tech, Inc.  
ATTN: S. Biola

Times Wire and Cable Co.  
ATTN: W. Primrose

TRW Defense & Space Systems  
ATTN: R. Baer  
ATTN: W. Lipner  
ATTN: R. Rathen  
ATTN: R. Eastman  
ATTN: J. Armstrong  
ATTN: A. Thomas  
ATTN: J. Larpe  
ATTN: R. Williams  
ATTN: T. Walter, Mr. Lott  
ATTN: J. Smith

TRW Defense & Space Systems  
ATTN: R. Baer

Valtec Corp.  
ATTN: L. Arnold

DATE  
FILMED  
— 8