

AD-A110 331

HONEYWELL POWER SOURCES CENTER MORSHAM PA
HIGH EFFICIENCY LITHIUM-THIONYL CHLORIDE CELL.(U)
JAN 82 N DODDAPANENI

F/6 10/3

DAAK20-81-C-0381


NL

UNCLASSIFIED

DELET-TR-81-0381-2

1 of 1
AD-A
10/1/82

END
DATE
FILMED
102-82
DTIC

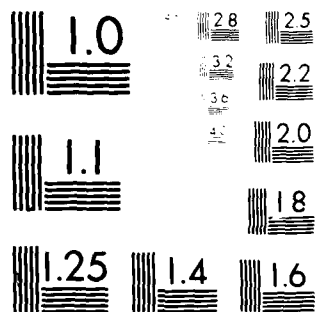

MICROCOPY RESOLUTION TEST CHART
NAT. BUREAU OF STANDARDS-1963-A



LEVEL III

(12)

A107447

Research and Development Technical Report

DELET-TR-82-0381-2

HIGH EFFICIENCY LITHIUM-THIONYL CHLORIDE CELL

Dr. N. Doddapaneni
Honeywell Power Sources Center
104 Rock Road
Horsham, PA 19044

DTIC
ELECTE
FEB 02 1982
S E

January 1982

SECOND QUARTERLY for PERIOD 9 JULY 1981 - 8 OCTOBER 1981

APPROVED FOR PUBLIC RELEASE: DISTRIBUTION UNLIMITED

Prepared for:

ELECTRONICS TECHNOLOGY AND DEVICES LABORATORY

DCASMA, PHILADELPHIA
P.O. BOX 7699
PHILADELPHIA, PA 19101

ERADCOM

US ARMY ELECTRONICS RESEARCH AND DEVELOPMENT COMMAND
FORT MONMOUTH, NEW JERSEY 07703

HISA-FM 195-78

36

AD A110331

FILE COPY

NOTICES

Disclaimers

The citation of trade names and names of manufacturers in this report is not to be construed as official Government indorsement or approval of commercial products or services referenced herein.

Disposition

Destroy this report when it is no longer needed. Do not return it to the originator.

HISA-FM-633-78

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER DELET-TR-81-0381-2	2. GOVT ACCESSION NO. AD-A110 331	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) High Efficiency Lithium-Thionyl Chloride Cell		5. TYPE OF REPORT & PERIOD COVERED Other 7-9-81 to 10-8-81
7. AUTHOR(s) N. Doddapaneni		6. PERFORMING ORG. REPORT NUMBER #2
9. PERFORMING ORGANIZATION NAME AND ADDRESS Honeywell Power Sources Center 104 Rock Road Horsham, Pa. 19044		8. CONTRACT OR GRANT NUMBER(s) / DAAK20-81-C-0381
11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army Elct Tech & Dvcs Laboratory ATTN: DELET-PR Fort Monmouth, NJ 07703		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 1L162705AH94-11-211
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) DCASMA, Philadelphia P.O. Box 7699 Philadelphia, Pa. 19101		12. REPORT DATE January 1982
		13. NUMBER OF PAGES 29
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Thionyl chloride, lithium, high discharge rates, low temperatures, catalysis, cyclic voltammetry		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Cathode polarization and discharge performance studies at -20 and -40°F showed that the limiting currents of Li/SOCl ₂ cells decreased linearly with reciprocal temperature and an Arrhenius temperature dependence of limiting current was not observed between the temperatures -40 and 75°F. Systematic evaluation of cathode variables such as carbon substrate, thickness and density on the cathode performance was carried out at 0°F		

408 275

32
Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

and 75°F. Significant improvements in both cathode polarization and performance were achieved with catalyzed cathodes containing 5% Teflon binder.

f
Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

TABLE OF CONTENTS

	<u>Page</u>
I. INTRODUCTION	1
II. EVALUATION OF CATHODE OVERPOTENTIAL	3
A. Laboratory Cell Measurements	3
1. Experimental	3
2. Half-Cell Measurements	3
3. Discharge Characteristics	9
B. Kinetic and Mechanistic Studies	9
III. CATHODE PERFORMANCE IMPROVEMENTS	12
A. Introduction	12
1. Carbon Substrates	12
2. Cathode Thickness	13
3. Cathode Density	13
B. Evaluation of Cathode Performance	16
1. Introduction	16
2. Discharge Performance	16
IV. SUMMARY AND FUTURE WORK	25
V. REFERENCES	26



Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By _____	
Distribution _____	
Availability Codes	
Dist	Avail or Special
A	

LIST OF FIGURES

	<u>Page</u>
1. Polarization Characteristics of Li/SOCl ₂ Cells at -20°F.	4
2. Polarization Characteristics of Li/SOCl ₂ Cells at -40°F.	5
3. Effect of Operating Temperature on Laboratory Li/SOCl ₂ Cell Limiting Current	6
4. Effect of Operating Temperature on Ln of Cell Limiting Current Density	7
5. Discharge Characteristics of Li/SOCl ₂ Cells at 5 mA/cm ² and -40°F.	8
6. Discharge Performance of Laboratory Li/SOCl ₂ Cells at 15 mA/cm ² and -40°F.	10
7. Discharge Characteristics of Li/SOCl ₂ Cells at 20 mA/cm ² and -20°F.	11
8. Flow Diagram of Cathode Fabrication Process	14
9. Effect of Teflon Content on the Cathode Density	15
10. Effect of Cathode Variables (Teflon Content) on the Discharge Performance of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte (50% Compressed Grade Shawinigan Acetylene Black Substrate)	17
11. Effect of Cathode Variable (Teflon Binder Content) on the Discharge Performance of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte (100% Compressed Grade Shawinigan Acetylene Black Substrate)	18
12. Effect of Cathode Variables on the Discharge Performance of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte [5% (CoPc) _n Doped 100% SAB Substrate]	19
13. Effect of Cathode Variables on the Discharge Performance of Li/SOCl ₂ with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte (A Comparison of Cathodes Fabricated with Different Substrates)	21
14. Effect of Cathode Variables on Voltage of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte at 10 mA/cm ² and 75°F.	22
15. Effect of Cathode Variables on the Discharge Performance of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte at 10 mA/cm ² and 0°F.	23
16. Effect of Cathode Variables on Voltage of Li/SOCl ₂ Cells with 1.5M LiAlCl ₄ /SOCl ₂ Electrolyte at 10 mA/cm ² and 0°F.	24

ABSTRACT

Cathode polarization and discharge performance studies at -20 and -40°F showed that the limiting currents of Li/SOCl_2 cells decreased linearly with reciprocal temperature and an Arrhenius temperature dependence of limiting current was not observed between the temperatures -40 and 75°F .

Systematic evaluation of cathode variables such as carbon substrate, thickness and density on the cathode performance was carried out at 0°F and 75°F . Significant improvements in both cathode polarization and performance were achieved with catalyzed cathodes containing 5% Teflon binder.

I. INTRODUCTION

The Li/SOCl_2 system (1-4) has the potential to be one of the best primary batteries having combined characteristics of high rate and high energy density capability, long shelf-life and wide operating temperature range. However, many of these advantages have not been fully derived. The operating capabilities of Li/SOCl_2 batteries are limited, to a large extent, by the Teflon bonded porous carbon electrode commonly used as a cathode. Cell failure at high discharge rates and/or low operating temperatures has, as one of its main causes, the high cathodic overpotential resulting from non-uniform current distribution over the porous electrode.

The porous carbon cathode, where the reduction of SOCl_2 occurs, has a limited capacity for retaining solid lithium chloride as it precipitates in the pore structure. As the lithium chloride accumulates, the porosity of the electrode is reduced to where mass transport, particularly of the cathode depolarizer, can no longer be maintained at a rate sufficient to support the required current density. When this happens, polarization becomes excessive and denotes the end of useful battery life.

At high rate discharges and low operating temperatures, the cathode polarization problem becomes very severe. Analysis of the porous electrode shows that, at high rate discharges, only a small part of the available surface participates in the electrochemical process.

Cathode polarization and the reaction zone thickness strongly depend on electrode reactions, cathode thickness and composition. Minimization of the effects of these variables on overpotential is essential in order for Li/SOCl_2 batteries to be viable electrochemical devices for many of the high rate/low temperature applications.

The objectives of this program, therefore, are to:

- a) Evaluate the polarization characteristics of Teflon-bonded porous carbon cathodes.
- b) Improve cathode performance at high discharge rates and low operating temperatures.

Polarization characteristics will be determined as a function of cathode thickness, composition and density, applied current density and temperature (-40°F to 75°F). Several experimental techniques such as half-cell measurements, discharge performance characteristics, impedance measurements, and cyclic voltammetry studies will be employed to evaluate the extent of each variable's contribution to the cathode polarization.

Improvement in cathode performance will be made by the use of electrocatalysis. Three catalysts to be employed in this program (5) have shown marked improvements in both cell voltage and cathode capacity. They are ^{*},

Catalyst A = Cobalt Phthalocyanine monomer, CoPc

Catalyst B = Iron Phthalocyanine monomer, FePc

Catalyst C = Polymeric Cobalt Phthalocyanine, (CoPc)_n

During the first quarter of this program, we examined:

- a) The overpotential of cathodes with and without Catalyst B and Catalyst C, over a temperature range of -40 to 75°F ,
- b) The effects of catalysts and temperatures on cyclic voltammograms in $\text{LiAlCl}_4/\text{SOCl}_2$ electrolyte solutions.
- c) The effects of operating temperatures (-40 to 75°F) on the conductivity and viscosity of the electrolyte solutions ($\text{LiAlCl}_4/\text{SOCl}_2$).

During this reporting period, we have completed the overpotential measurements at -20 and -40°F on our present baseline cathodes with and without catalysts. These cathodes contained 5% Teflon binder and had a thickness of 0.020 inch. Furthermore, we have systematically evaluated the effect of cathode thickness, amount of Teflon binder and cathode substrates, on the cathode performance. The two types of carbon substrates examined were:

- a) 50% compressed grade Shawinigan Acetylene Black (50% SAB), and
- b) 100% Compressed grade Shawinigan Acetylene Black (100% SAB).

In addition, the effect of catalyst doping in 100% SAB was evaluated.

^{*} Patents pending

II. EVALUATION OF CATHODE OVERPOTENTIAL

A. LABORATORY CELL MEASUREMENTS

1. Experimental

The laboratory cell design and the description of cell components used in the evaluation of cathode overpotential presented here are described in the first quarterly report (6).

2. Half-Cell Measurements

The effect of operating the Li/SOCl₂ cells at -20 and -40°F on the cathode overpotential was examined. In addition, the effect of catalyst doping [FePc and (CoPc)_n] on the cathode polarization was evaluated. The potential dependence of the current was determined by measuring the steady-state potential versus the lithium reference electrode at various controlled currents.

The polarization characteristics of three electrodes (one baseline and two catalyst doped) were examined at operating temperatures of -20 and -40°F and the results were plotted in Figures 1 and 2, respectively. Electrolyte insoluble (CoPc)_n catalyst doping was achieved by impregnating the catalyst onto 100% SAE from a concentrated H₂SO₄ solution whereas FePc doping was carried out by dissolving it in the electrolyte before Li/SOCl₂ cells with baseline cathodes were activated. The cathode density and surface area for baseline cathodes and FePc doped cathodes in Li/SOCl₂ were, therefore, equal. However, only a slight difference in cathode density and surface were observed with (CoPc)_n doped cathodes when compared to the baseline cathode.

Catalyzed cathodes reduced the cathode polarization significantly. This effect was anticipated and the activation polarization associated with SOCl₂ adsorption and electron transfer processes was minimized by electrocatalytic reduction of SOCl₂. However, the electrode polarization increases as the operating temperature decreases. And also, Li/SOCl₂ cell limiting current decreases with decreasing temperatures. The relationships between the limiting current, limiting current density and operating temperatures were plotted in Figures 3 and 4, respectively.

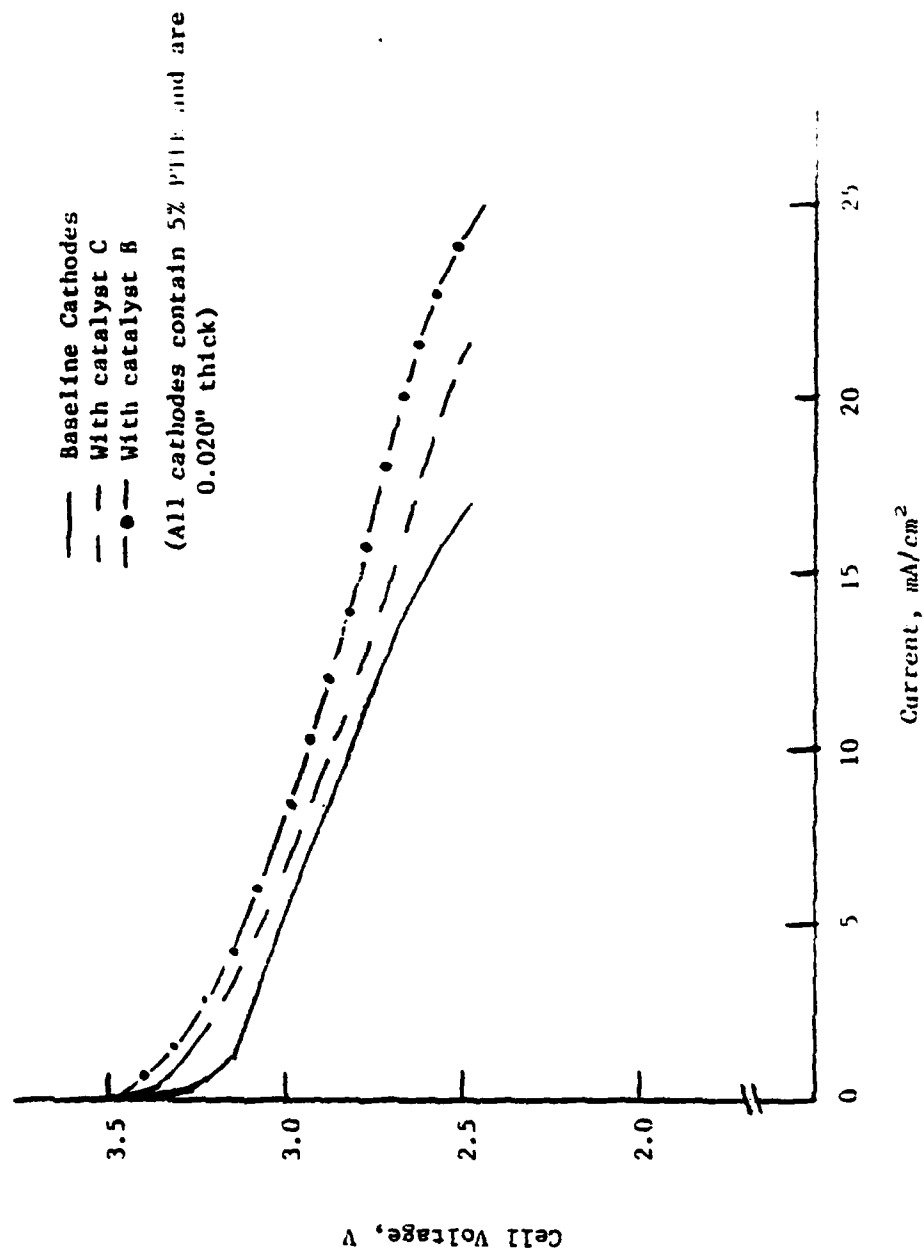


Figure 1. Polarization Characteristics of Li/SOCl₂ Cells at -20°F.

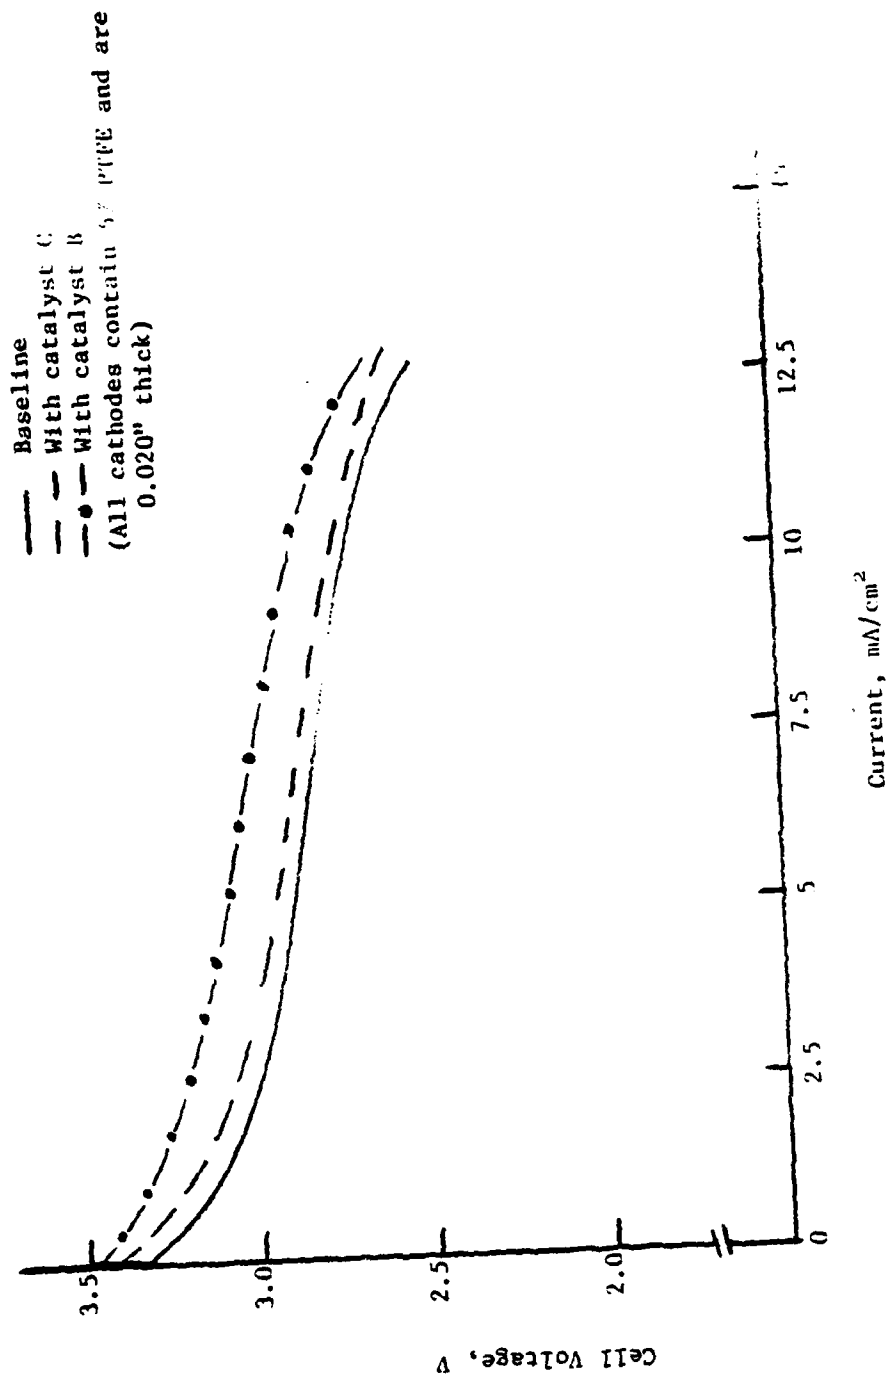


Figure 2. Polarization Characteristics of Li/SOCl₂ Cells at -40°C

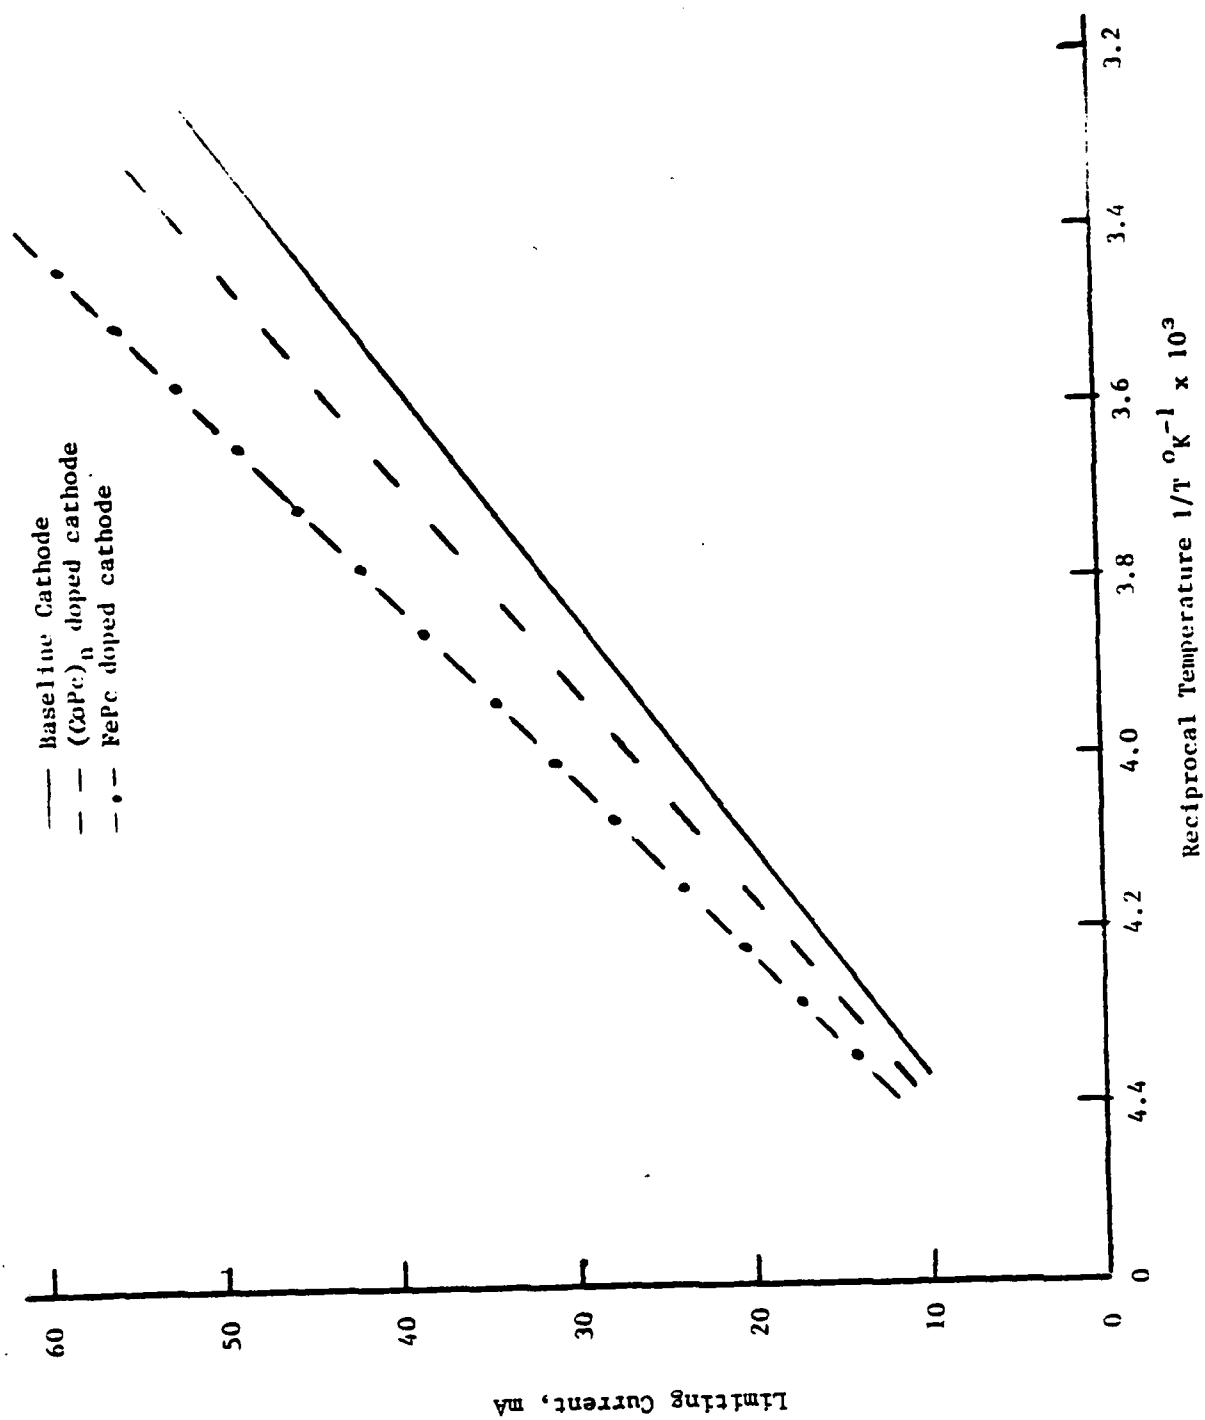


Figure 3. Effect of Operating Temperature on Laboratory Li/SOCl₂ Cell Limiting Current

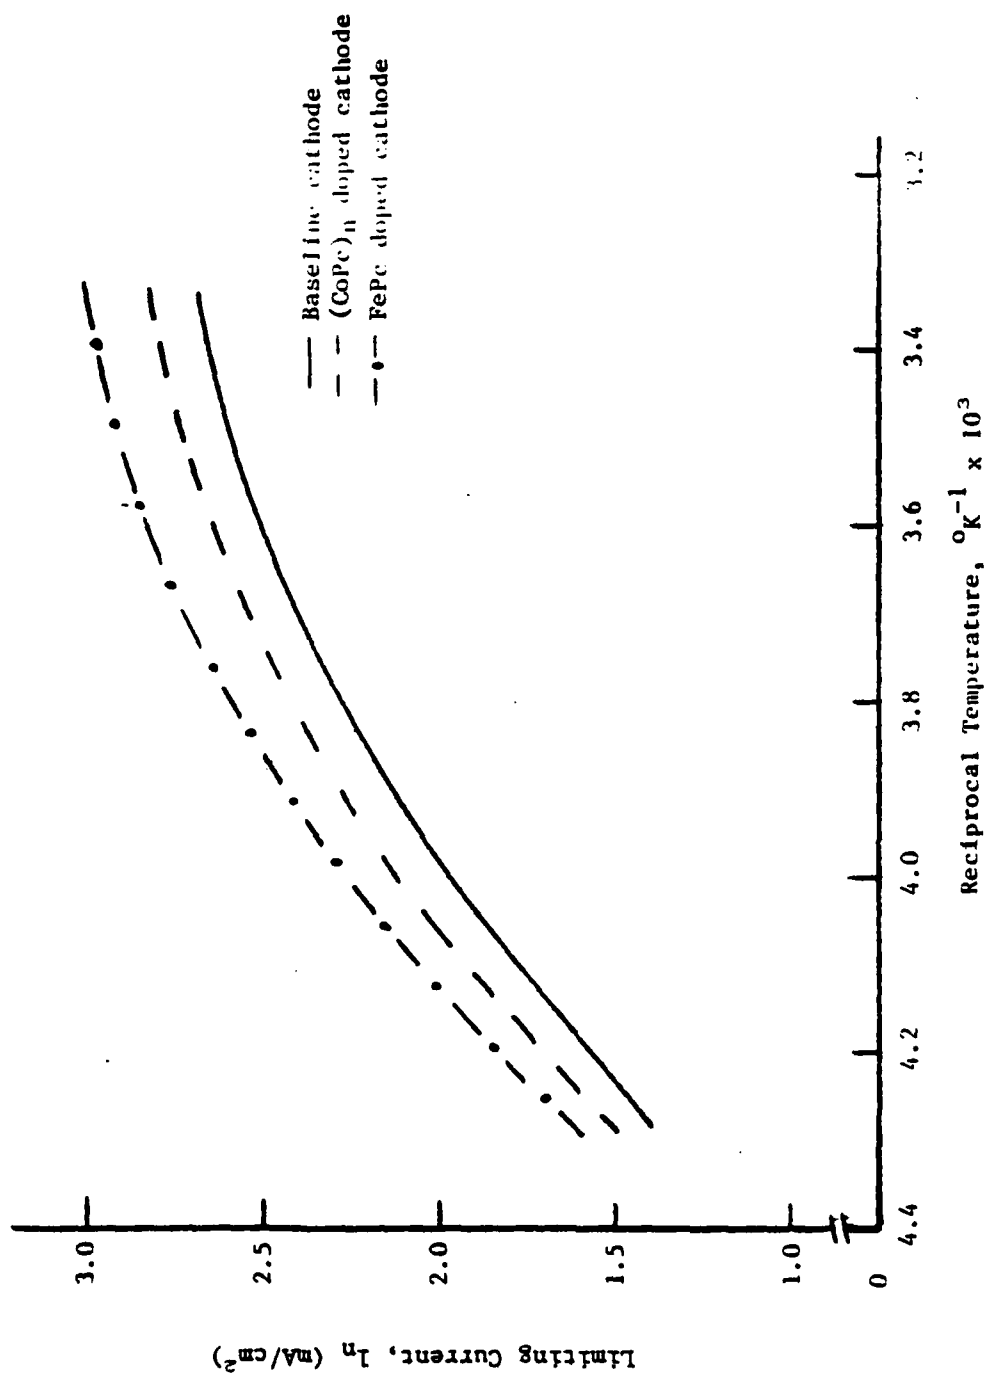


Figure 4. Effect of Operating Temperature on $\ln$ of Cell Limiting Current Density

A linear relationship between limiting current and reciprocal temperature (Figure 3) exists for all three types of cathodes. It is interesting to note that a similar relationship between electrolyte conductivity and reciprocal temperature exists as reported in the first quarterly report. An Arrhenius-type temperature dependency of limiting current was not observed as shown in Figure 4. As the temperature decreases, the slope of the curve increases indicative of changes in the mass transport rates. Beside mass transport problems of cathode depolarizer, electrochemical product adsorption on the carbon surface and glass mat separator porosity contribute to the lowering of Li/SOCl_2 limiting current at low operating temperatures.

3. Discharge Characteristics

Discharge performance of Li/SOCl_2 cells at -20 and -40°F were studied. Cells were activated at room temperature and then cooled to appropriate temperatures. During cooling period, the cells were kept under a constant current load of 0.2 mA/cm^2 in order to avoid passivation problems.

In Figure 5, the discharge characteristics corresponding to current density of 20 mA/cm^2 in Li/SOCl_2 cells using three different cathodes were compared. Cathode performance at 5 and 10 mA/cm^2 at -20°F was reported in (6). A significant cathode polarization is observed without catalyst at 20 mA/cm^2 rate.

At operating temperature of -40°F , the Li/SOCl_2 cells with baseline cathodes cannot support a discharge current density of 20 mA/cm^2 for more than a few minutes. For this reason, the cells were discharged at 5 and 15 mA/cm^2 . Dramatic improvements in cathode performance and cell voltage were obtained with catalyzed cathodes as shown in Figures 6 and 7.

B. KINETIC AND MECHANISTIC STUDIES

Cyclic voltammetric and rotating disc electrode studies in $1.0\text{M LiAlCl}_4/\text{SOCl}_2$ solution at various cathode surfaces were continued. Initial results obtained with rotating disc electrode (glassy carbon) showed problems with reproducibility. Therefore, it is planned to employ pressure annealed pyrolytic graphite and platinum as rotating disc electrodes. Presently these electrodes are being fabricated and further studies will be made in the next quarter.

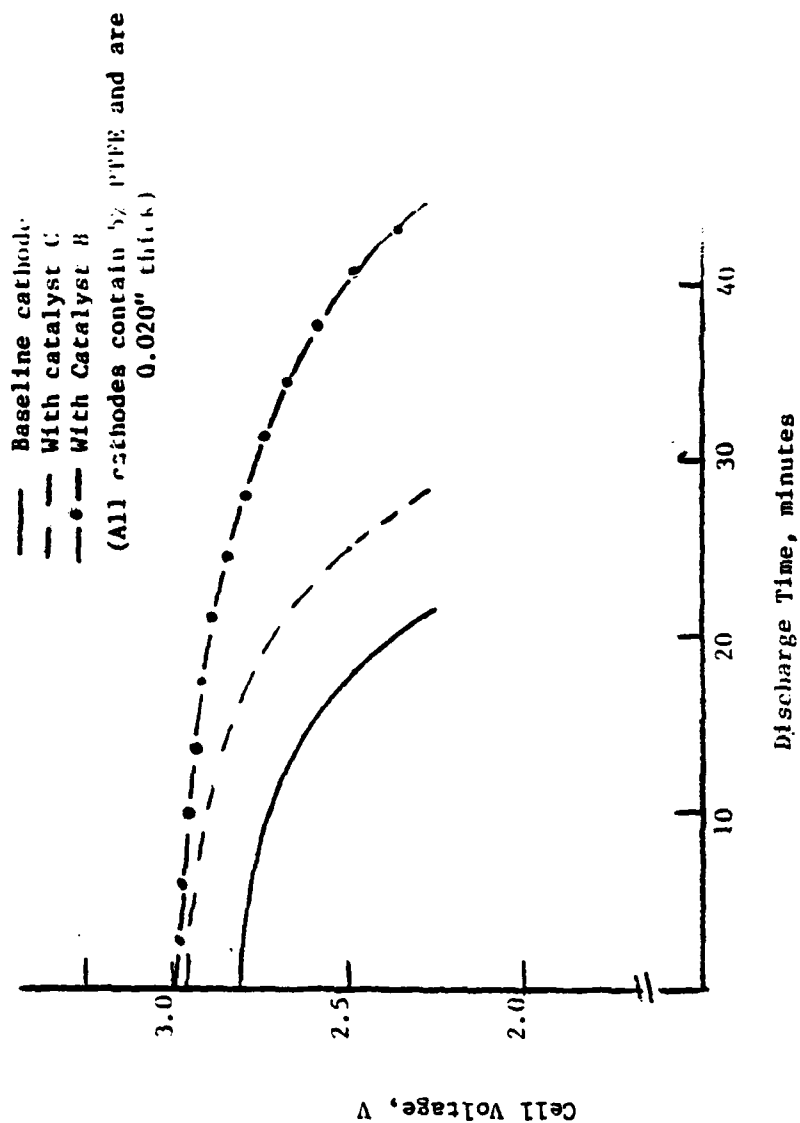


Figure 5. Discharge Characteristics of Li/SOCl₂ Cells at 20 mA/cm² and -20°C

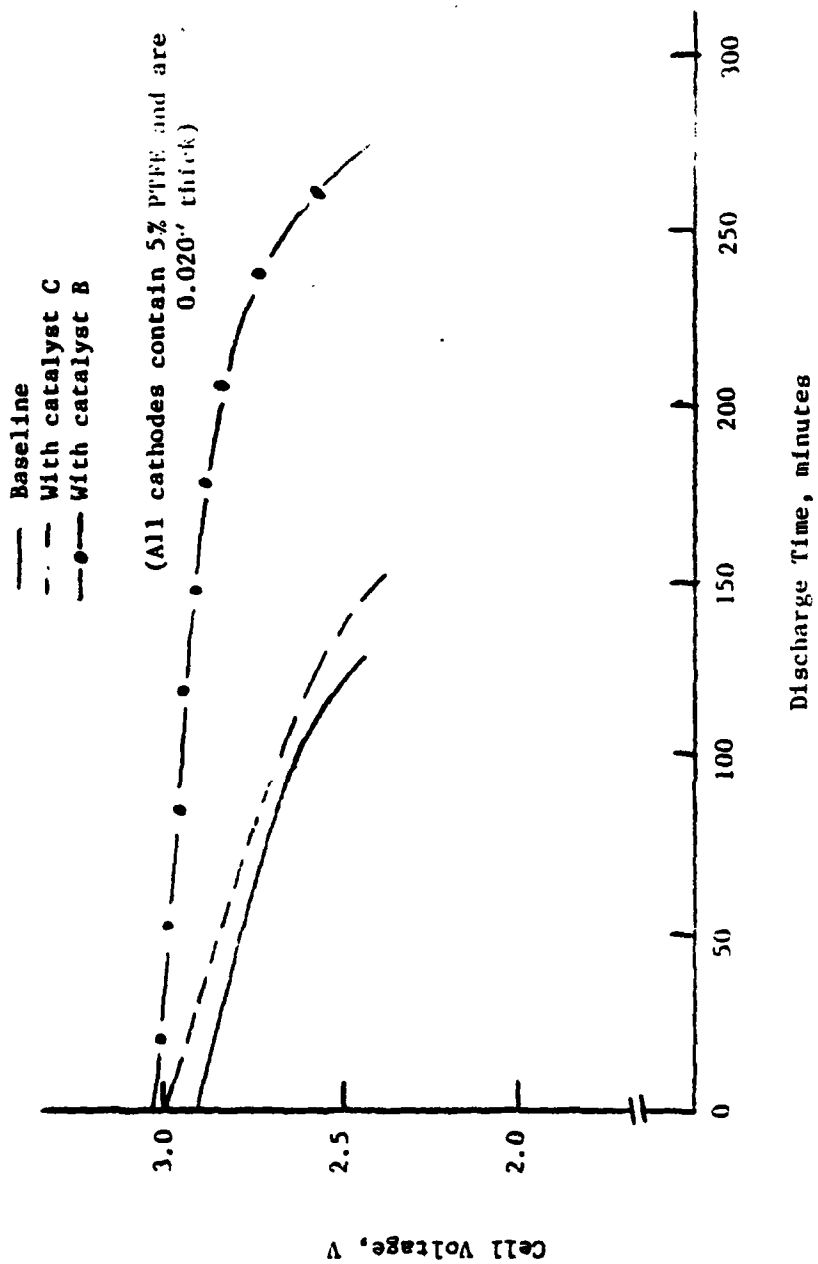


Figure 6. Discharge Characteristics of Li/SOCl₂ cells at 5 mA/cm² and -40°F.

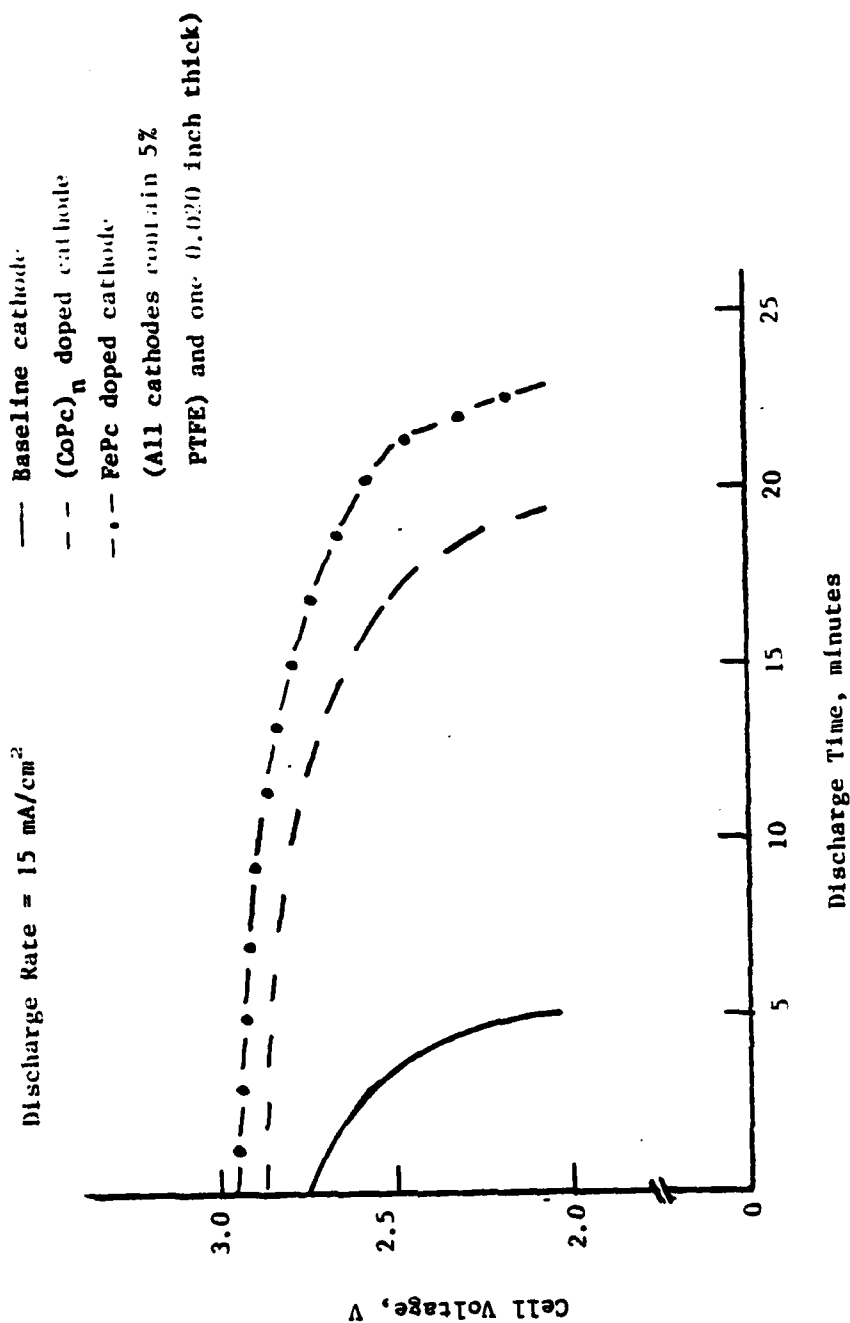


Figure 7. Discharge Performance of Laboratory Li/SOCl₂ Cells at 15 mA/cm^2 and -40°F .

III. CATHODE PERFORMANCE IMPROVEMENTS

A. INTRODUCTION

The electrochemical reduction of thionyl chloride takes place at the cathode surface and the reduction rate is known to depend strongly on the cathode material. The widely accepted cathode reaction



proceeds smoothly at low rates upon various metals and non-metals, but it has been found that high rates can be achieved only by using carbon black substrates doped with or without electrocatalysts (5). Properties such as surface area, particle size, density, conductivity, etc., of the carbon influence, to a varying degree, its ability to enhance the rate of SOCl_2 reduction.

Cathode polarization and the electrochemical reaction zone thickness strongly depend on electrode reactions, cathode thickness and composition. Minimization of the effects of these variables on cathode polarization and performance are essential in order for Li/SOCl_2 batteries to be viable electrochemical devices for many of the high rate/low temperature applications. Therefore, during this reporting period, three cathode variables were studied to optimize the cathode performance. They are:

- 1) Carbon substrates
- 2) Cathode thickness
- 3) Cathode density

1. Carbon Substrates

Since it is known that acetylene black carbons catalyze the SOCl_2 reduction better than any other carbon reported in the literature, we examined both 50% and 100% compressed grade Shawinigan acetylene blacks (SAB) for their effect

on cathode performance. In addition, the catalytic effect of $(\text{CoPc})_n$ and FePc catalysts were examined. These catalysts were doped only on 100% SAB because of its superior performance observed over 50% SAB. The catalyst doping method was described elsewhere(6).

2. Cathode Thickness

At high discharge rates, only a small part of the available cathode surface participates in the electrochemical SOCl_2 reduction process at porous teflonated carbon cathodes. This part of the electrode structure is often referred to as the reaction zone. The reaction zone thickness is influenced by both kinetics and mechanism of electrochemical reduction. In addition, cathode thickness effects the reaction zone (depth of penetration). Therefore, the effect of cathode thickness on both voltage and performance of cathode were studied. Cathodes of thickness, 0.010, 0.015, 0.020, 0.030 and 0.040 inches were fabricated for each substrate described above. The standard cathode fabrication process was summarized in Figure 8.

3. Cathode Density

The cathode in the Li/SOCl_2 system uses porous teflonated carbon electrodes. The amount of Teflon binder influences the cathode density, conductivity, surface area, etc. Therefore, in order to optimize the Teflon amount on these physical properties which influence the cathode performance, cathodes were fabricated containing 5, 10 and 15% by weight Teflon binder. In Figure 9, cathode density dependence on the Teflon content was plotted for three different carbon substrates. Approximately 20% increase in cathode density is observed with 100% SAB compared to that of cathode with 50% SAB substrate. The drop in density with 5% $(\text{CoPc})_n$ doped 100% SAB might be due to porosity created during heat treatment at $550 - 600^\circ\text{C}$.

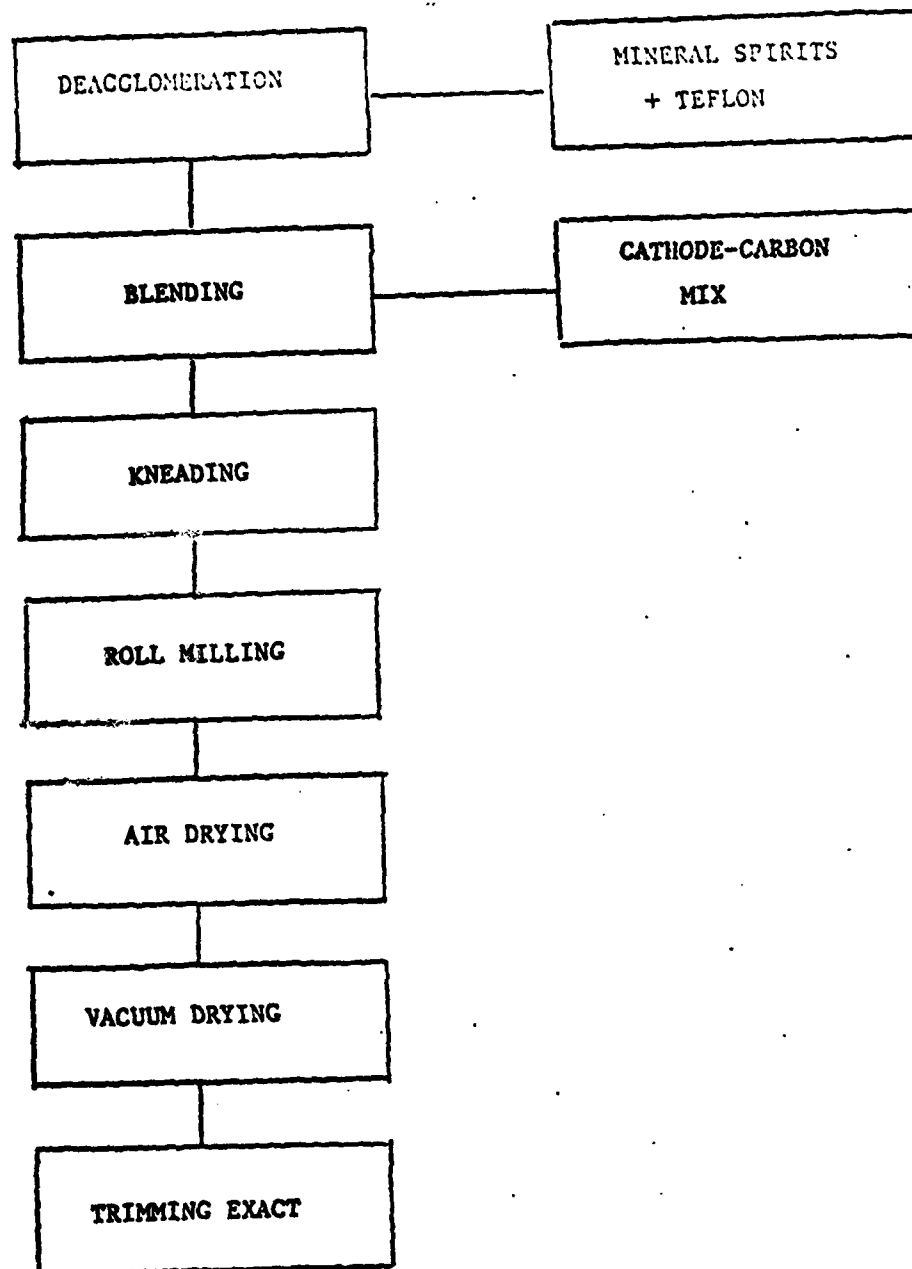


Figure 8. Flow Diagram of Cathode Fabrication Process. Workability of the process not restricted to specific carbon type. Rolling incurs excellent mechanical integrity on the cathode.

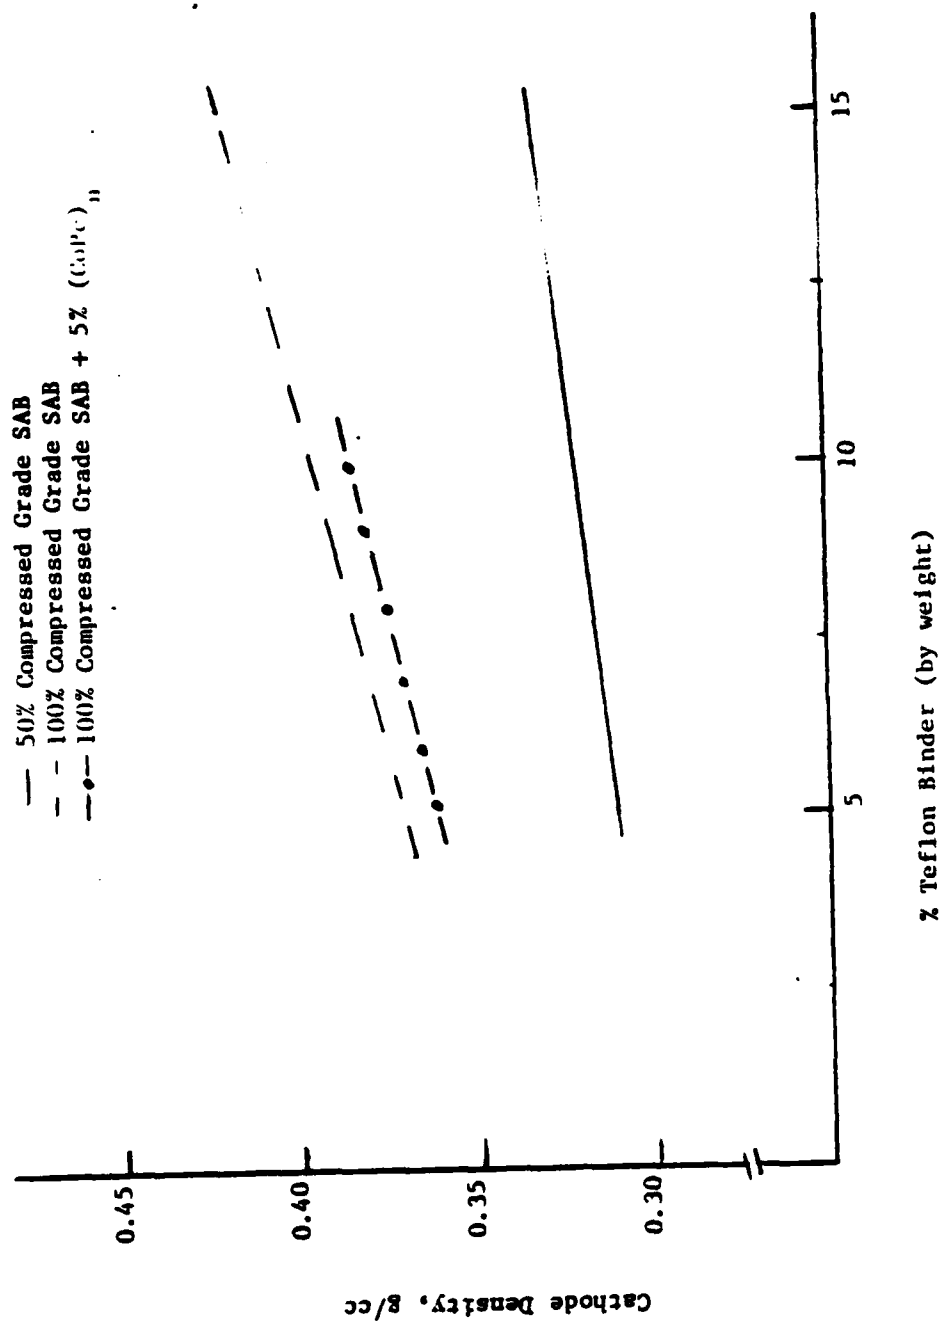


Figure 9. Effect of Teflon Content on the Cathode Density

B. EVALUATION OF CATHODE PERFORMANCE

1. Introduction

Cathode performance was evaluated by discharging laboratory Li/SOCl₂ cells at a fixed 10 mA/cm² current rate. The effect of cathode substrate, thickness and density, and the temperature on the discharge performance were examined. Performance evaluation of two operating temperatures (0°F and 75°C) was carried out during the reporting period. All cells were activated at ambient temperature and cooled to appropriate temperature with a constant current load equivalent to 0.2 mA/cm² to avoid passivation problems associated with Li/SOCl₂ system. All experiments were duplicated and if a variation was found, it was repeated until reproducible results were obtained. A total of 40 cathodes were fabricated and evaluated.

2. Discharge Performance

Discharge characteristics were studied in our standard laboratory cell fixture. Cells were discharged with a constant current load equivalent to 10 mA/cm² using a Hewlett-Packard DC current source (#6181B). In order to maintain identical experimental conditions, cells containing cathodes of constant density were built and discharged together for every operating temperature. For example, cathodes having thicknesses of 0.010, 0.015, 0.020, 0.030 and 0.040 inches, fabricated from a carbon mix containing 5% Teflon binder and 50% SAB, were evaluated in duplicate together at 0°F. This procedure maintained a constant cooling time and exposed the cells to the same fluctuations in temperature and discharge rate.

In Figures 10 - 12, the effect of cathode density on the discharge performance of cathodes fabricated from 50% SAB, 100% SAB and 5% (CoPc)_n doped 100% SAB were given, respectively. No significant change in performance was observed (Figure 10) with 50% compressed grade Shawinigan acetylene black cathode substrate containing 5 - 15% Teflon binder. However, cathodes fabricated with 100% SAB with and without (CoPc)_n catalyst showed best performance with 5% Teflon binder (Figures 11 and 12). Similar behavior was observed for FePc catalyzed cathodes.

Discharge Rate = 10 mA/cm²
 Operating Temp = 75°F

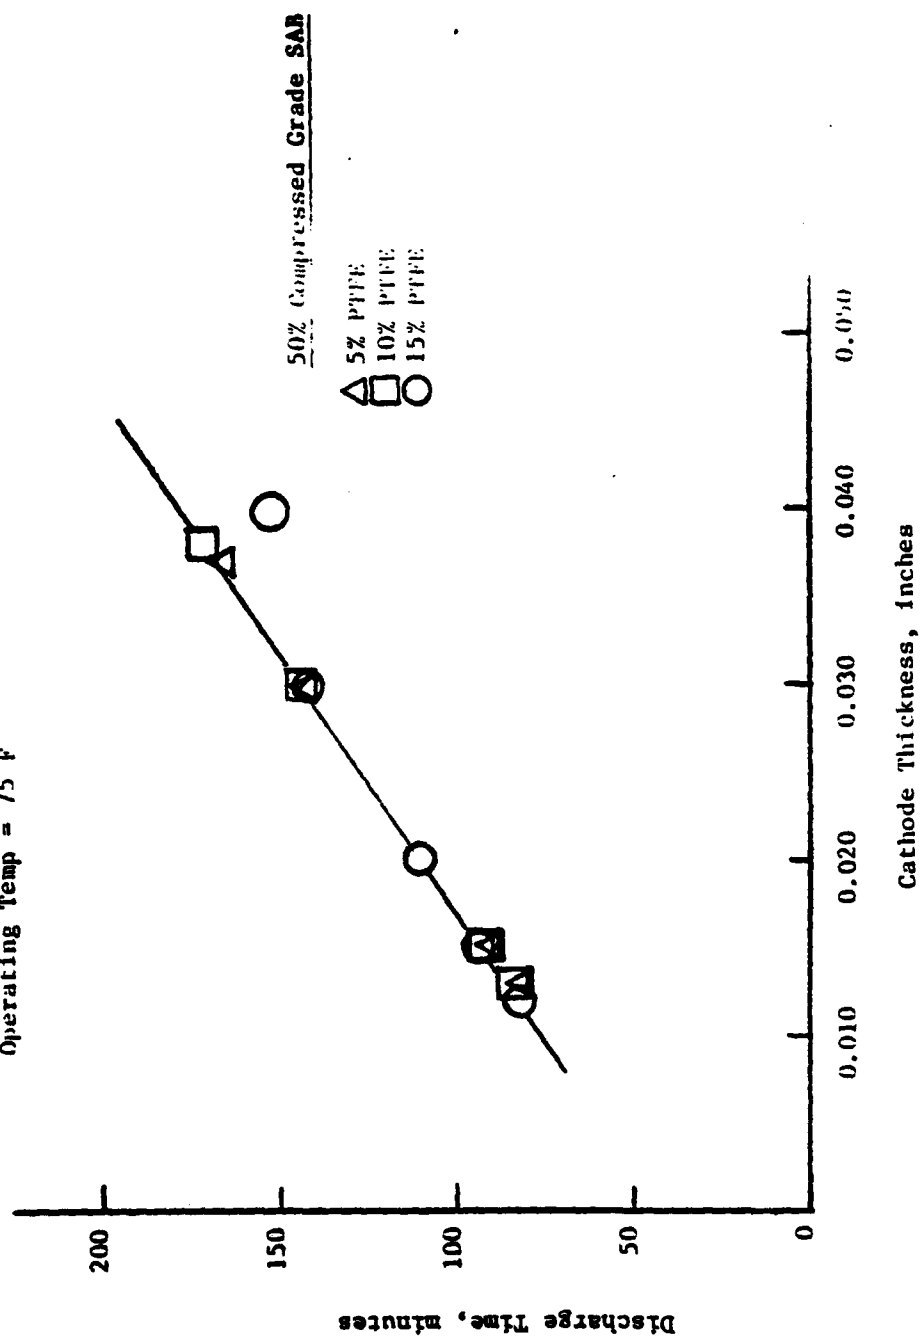


Figure 10. Effect of Cathode Variables (Teflon Content) on the Discharge Performance of Li/SOCl₂ Cells with 1.5M LiAlCl₄/SOCl₂ Electrolyte

Discharge Rate = 10 mA/cm^2
 Operating Temp = 75°F

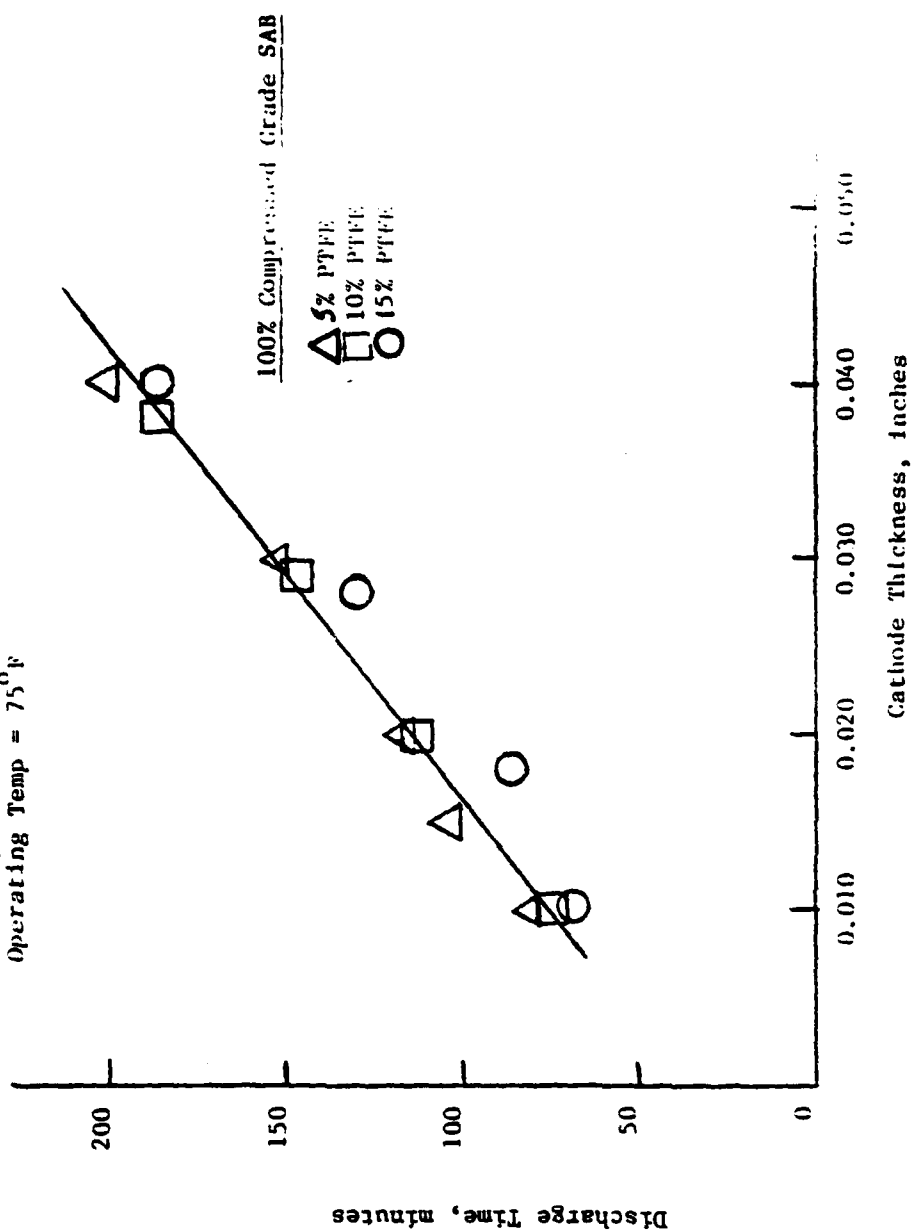


Figure 11. Effect of Cathode Variable (Teflon Binder Content) on the Discharge Performance of Li/SOCl_2 Cells with $1.5\text{M LiAlCl}_4/\text{SOCl}_2$ Electrolyte

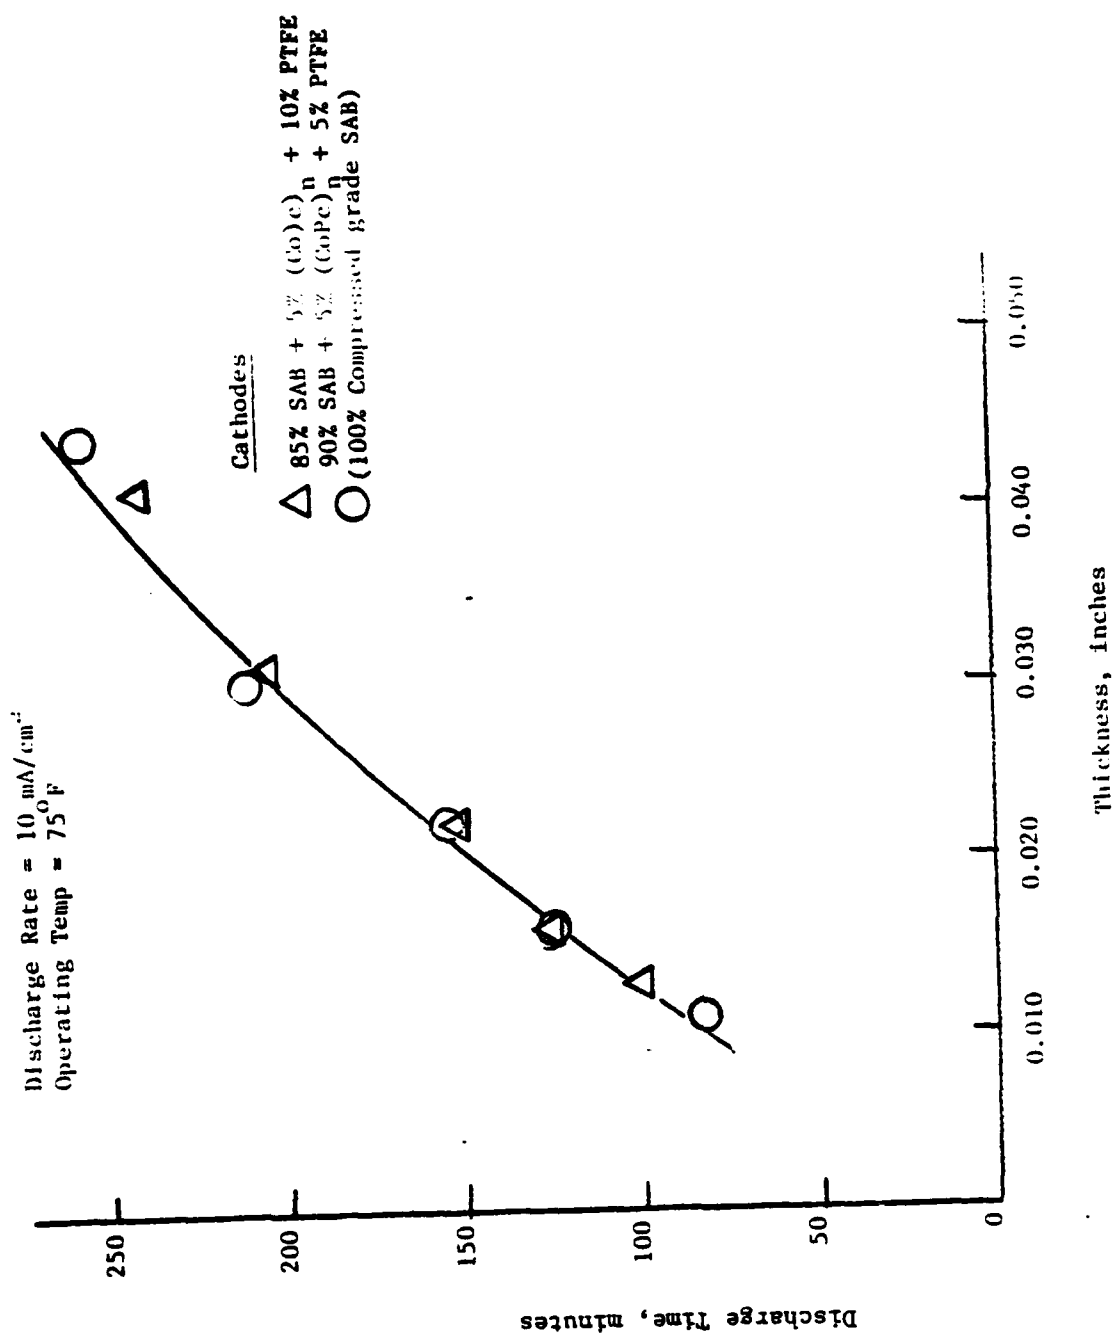


Figure 12. Effect of Cathode Variables on the Discharge Performance of Li/SOCl₂ Cells with 1.5M LiAlCl₄/SOCl₂ Electrolyte

The discharge performance of cathodes fabricated from various substrates was compared in Figure 13. All the cathodes contained 5% Teflon binder and the cells were discharged at ambient temperature with a constant current load equivalent to 10 mA/cm^2 . Significant performance improvements were achieved with catalyzed cathodes. As the cathode thickness increases, the improvement in cathode performance increases with catalyzed cathodes. However, the slope decreases with cathode thickness regardless of cathode substrate.

In Figure 14, the cell voltage at 50% depth-of-discharge with respect to cathode cell thickness was compared for the cells described in Figure 13. The cell voltage remained constant for cathodes containing 50% SAB whereas all other increased with cathode thickness. Dramatic voltage improvements were achieved with FePc catalyzed cathodes.

Low temperature (0°F) performance of cells described in Figure 13 was given in Figures 15 and 16. In general, lowering the temperature resulted in a decrease in electrochemical cell performance irrespective of cathode thickness and cathode substrate (Figure 15). However, with the uncatalyzed cathodes, the cell voltage improved significantly (Figure 16) with cathode thickness. Furthermore, the cell voltage of $(\text{CoPc})_n$ catalyzed cathodes exhibited a lesser decrease. This can be seen when both Figures 14 and 16 are compared. The significance of this observation will be better understood when the performance is evaluated at -20 and -40°F .

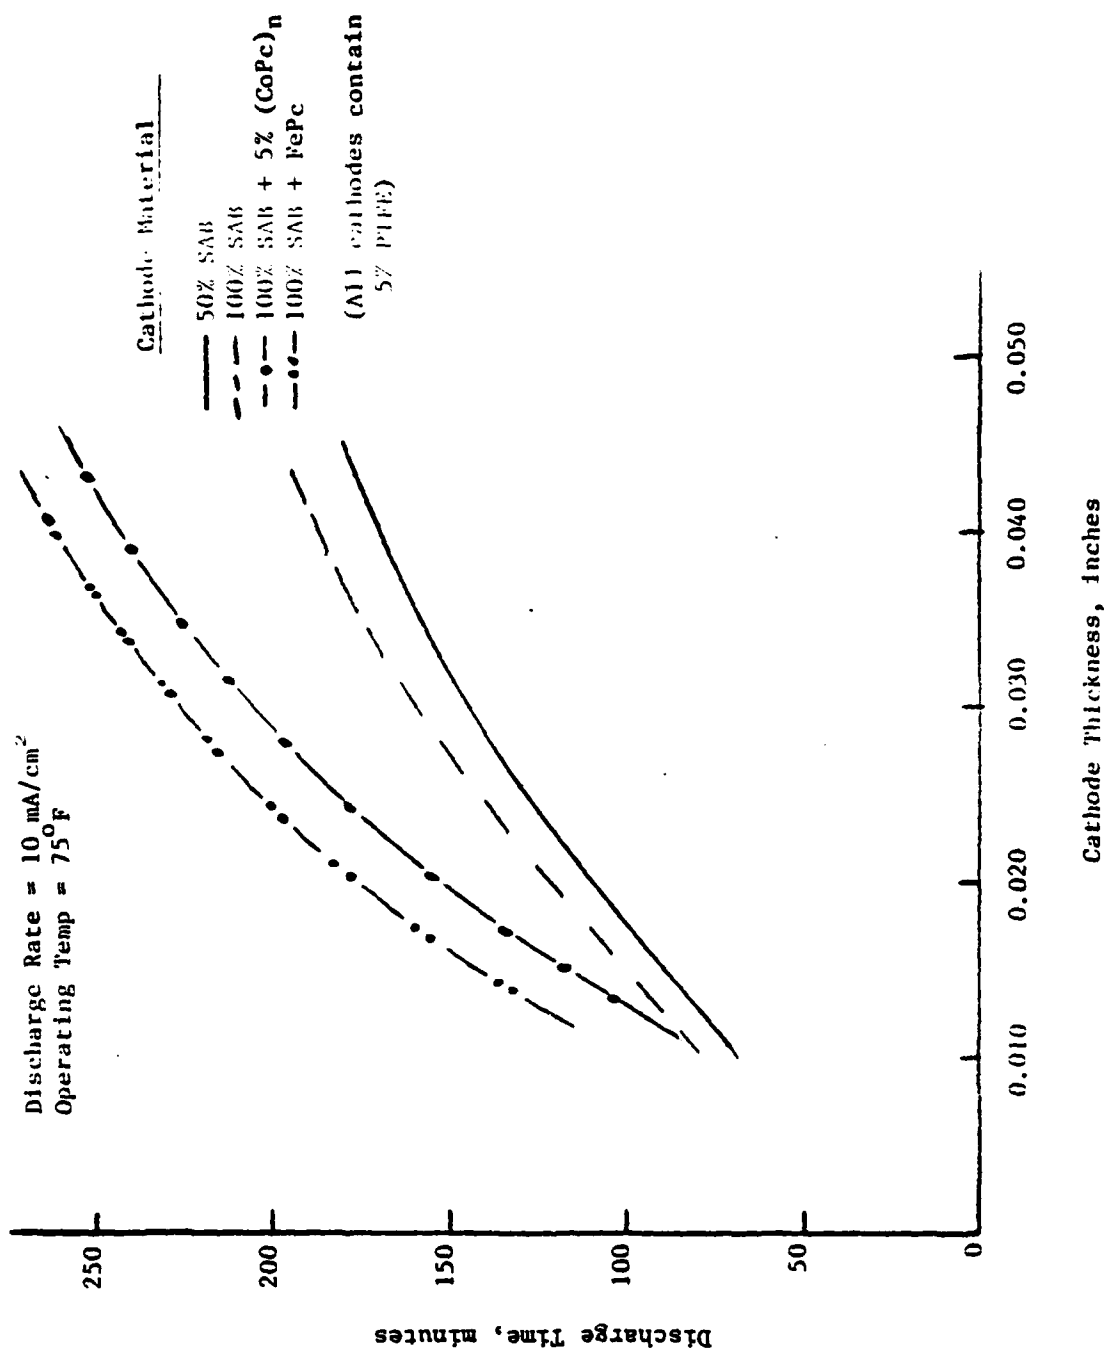


Figure 13. Effect of Cathode Variables on the Discharge Performance of Li/SOCl₂ with 1.5M LiAlCl₄/SOCl₂ Electrolyte

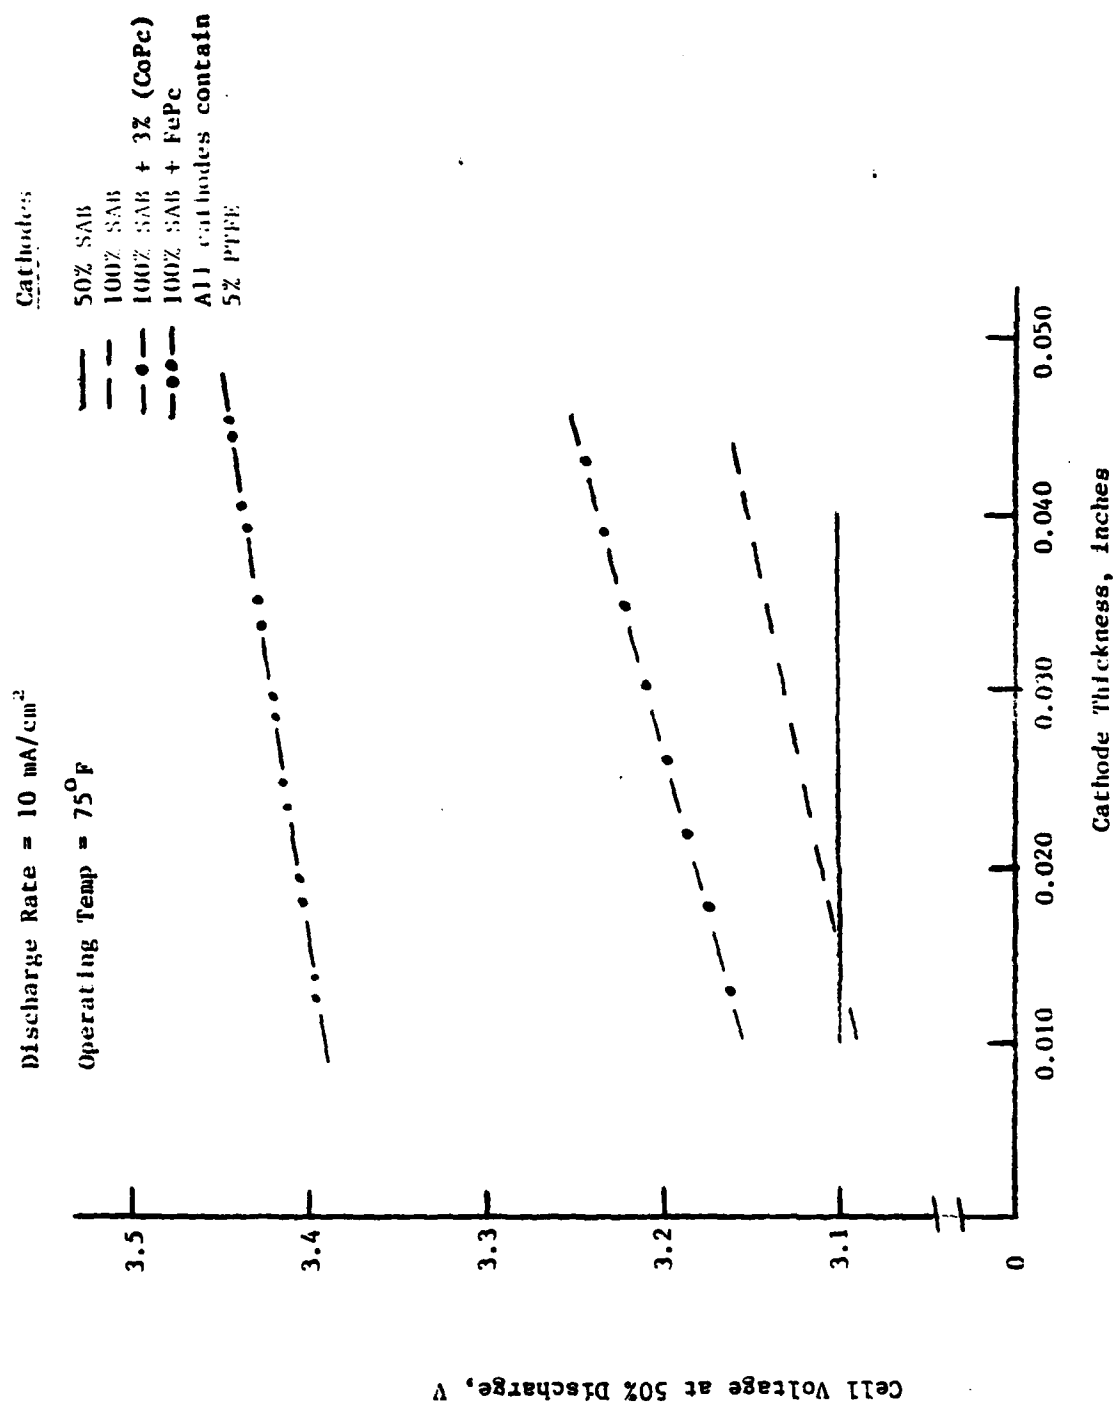


Figure 14. Effect of Cathode Variables on Voltage of LiI/SOCl₂ Cells with 1.5M LiAlCl₄/SOCl₂ Electrolyte at 10 mA/cm² and 75°F.

Discharge Rate = 10 mA/cm²
 Operating Temp = 0°F

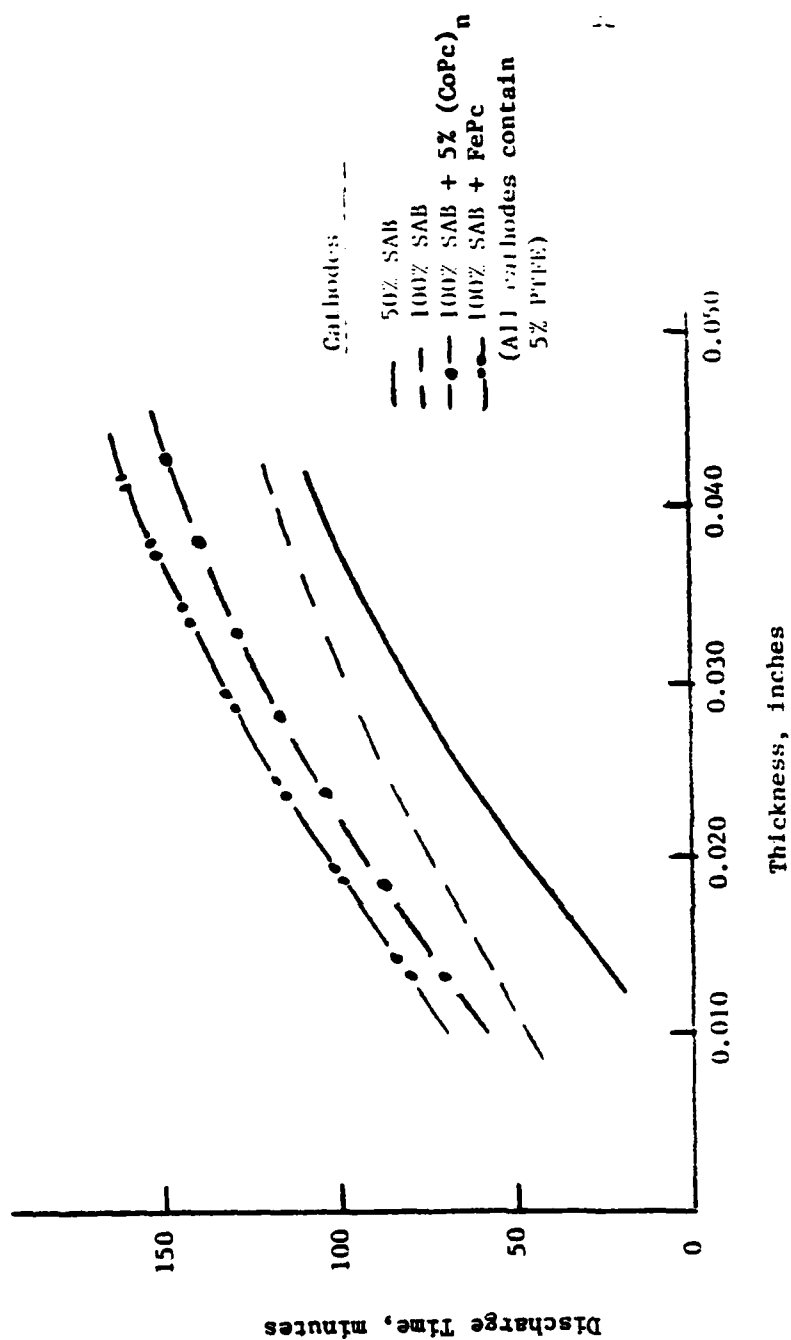


Figure 15. Effect of Cathode Variables on the Discharge Performance of Li/SOC (Cells with 1.5M LiAlCl₄/SOCl₂ Electrolyte at 10 mA/cm² and 0°F.

Discharge Rate = 10 mA/cm²

Operating Temp = 0°F

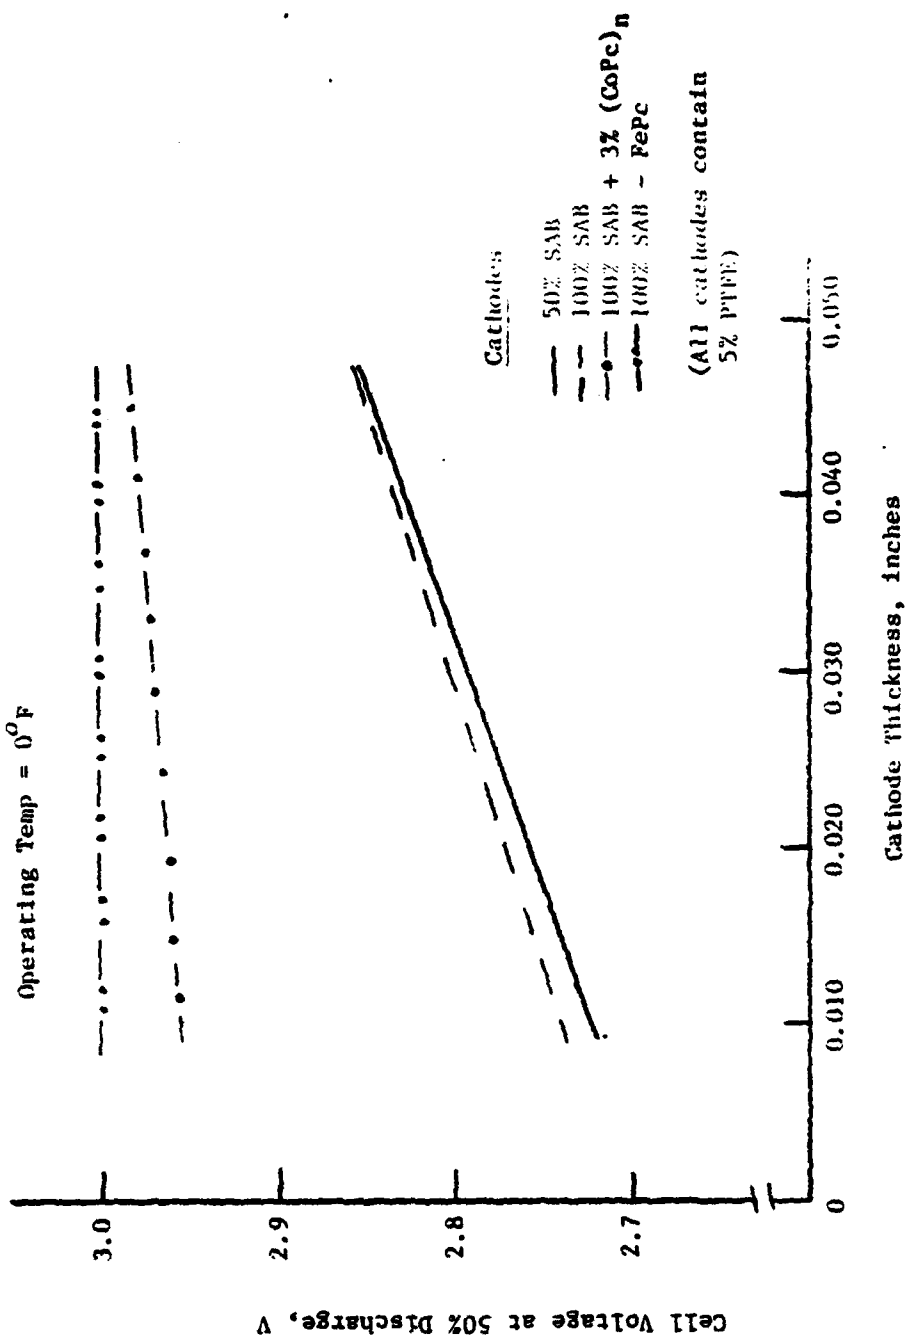


Figure 16. Effect of Cathode Variables on Voltage of Li/SOCl₂ Cells with 1.5M LiAlCl₄/SOCl₂ Electrolyte at 10 mA/cm² and 0°F.

IV. SUMMARY AND FUTURE WORK

Polarization and discharge performance characteristic of our best baseline cathodes with and without catalysts such as $(\text{CoPc})_n$ and FePc were studied at operating temperatures of -20 and -40°F . Both cathode overpotential and performance were affected by the operating temperature and a linear relationship between cell limiting currents and reciprocal temperature was observed.

The effect of cathode substrate material, thickness and density on discharge performance were evaluated at 0°F and 75°F . It was found that 100% compressed grade Shawinigan acetylene black (SAB) is superior to 50% SAB. Furthermore, catalyzed cathodes improved both cell voltage and cathode performance. Irrespective of cathode substrate material, the cathodes containing 5% Teflon binder performed better.

During the next quarter, effect of cathode variables on discharge performance will be evaluated at -20 and -40°F . Kinetic and mechanistic studies of SOCl_2 reduction will be continued. Impedance measurements will be made on best cathodes selected after our cathode variable study.

V. REFERENCES

1. W. K. Behl, J. A. Christopoulos, S. Ramirez and S. Gilman, J. Electrochem. Soc. 120, 1619 1973.
2. J. J. Auburn, K. W. Prech, S. I. Lieberman, V. K. Shah and A. Heller, J. Electrochem. Soc. 120, 1613 1973.
3. G. E. Blomgren, V. Z. Leger, T. Kalnoki-Kis, M. L. Kronenberg and R. J. Brodd, in "Power Sources", J. Thomson, Editor, p. 583, Academic Press (1979).
4. A. N. Dey, Thin Solid Films, 43, 131 (1977).
5. N. Doddapaneni, Abstract No. 83 presented at National Electrochemical Society, Spring Meeting, Minneapolis, MN, May 10 - 15, 1981.
6. N. Doddapaneni, High Efficiency Lithium-Thionyl Chloride Cell, First Quarterly Report, DELET-TR-81-0381-1. Honeywell Power Sources Center, October 1981.

DISTRIBUTION LIST

Defense Technical Info Ctr ATTN: DTIC-TCA Cameron Station (Bldg 5) Alexandria, VA 22314	(12)	Commander US Army Electronics R&D Command Fort Monmouth, NJ 07703	
Cdr, Naval Surface Weapons Ctr White Oak Laboratory ATTN: Library, Code WX-21 Silver Spring, MD 20910	(1)	DELET-DD DELET-DT DELS-D-L (Library) DELS-D-L-S (Stinfo) DELET-PR (W. Behl)	(1) (1) (1) (2) (18)
Commandant, Marine Corps HQ, US Marine Corps ATTN: Code LMC, INTS (In Turn) Washington, DC 20380	(1)	NASA Scientific & Tech Info Facility Baltimore/Washington Intl Airpt PO Box 8757, MD 21240	(1)
Rome Air Development Center ATTN: Documents Library (TSLD) Griffiss AFB, NY 13441	(1)	CMDR, MICOM ATTN: DRCPM-HDE Redstone Arsenal, AL 35809	(1)
AFGL/SULL S-29 HAFB, MA 01731	(1)	Foote Mineral Company Route 100 Exton, PA 19341 ATTN: Dr. H. Grady	(1)
HQDA (DAMA-ARZ-D/Dr. F.D.Verderame) Washington, DC 20310	(1)	Eagle-Picher Industries, Inc. Electronics Division P.O. Box 47 Joplin, Missouri 64801 ATTN: Mr. Robert L. Higgins	(1)
Cdr, Harry Diamond Laboratories ATTN: Library 2800 Powder Mill Road Adelphia, MD 20783	(1)	Yardney Electric Company 82 Mechanic Street Pawcatuck, CT 06379 ATTN: Technical Library	(1)
Director US Materiel Sys Anal Actv ATTN: DRXSY-T Aberdeen Prov Grnd, MD 21005	(1)	Duracell International, Inc. Northwest Industrial Park Burlington, MA 01803 ATTN: Dr. A.N. Dey	(1)
Cdr, USA Signals Warfare Lab ATTN: DELSW-OS Vint Hill Farms Station Warrenton, VA 22186	(1)	Exxon Research & Engineering Co. Corporate Research Laboratory Linden, NJ 07036 ATTN: Dr. R. Hamlen	(1)
Commander USA Mobility Eqp Res & Dev Cmd ATTN: DRDME-R Fort Belvoir, VA 22060	(1)	Argonne National Laboratories 9700 South Cass Argonne, IL 60439 ATTN: Dr. E.C. Gay	(1)

GTE Sylvania, Inc.
77 A Street
Needham Heights, MA 02194
ATTN: Mr. Richard Pabst

(1)

General Motors Corp.
Research Laboratories
General Motors Technical Center
12 Mile and Mounds Roads
Warren, MI 48090
ATTN: Dr. J.L. Hartman

(1)

Union Carbide Corporation
Parma Research Center
P.O. Box 6116
Cleveland, OH 44101

(1)

Duracell International, Inc.
S. Broadway
Tarrytown, NY 10591
ATTN: J. Dalfonso

(1)

North American Rockwell Corp.
Atomics International Division
Box 309
Canoga Park, CA 91304
ATTN: Dr. L. Heredy

(1)

General Electric Research &
Development Center
P.O. Box 8
Schenectady, NY 12301
ATTN: Dr. Stefan Mitoff

(1)

University of California
Department of Science & Research
Santa Barbara, CA 93100
ATTN: Dr. J. Kennedy

(1)

Gulton Industries, Inc.
Metuchen, NJ 08840
ATTN: Mr. S. Charlip

(1)

INCO Research and Development
Center
Sterling Forest
Suffern, NY 10901
ATTN: Nehemiah Margalit

(1)

Director
Propulsion and Power Division
Mail Code EP5
NASA-Johnson Space Center
Houston, Texas 77058
ATTN: Mr. B. J. Bragg

(1)

GTE Laboratories, Inc.
520 Winter Street
Waltham, MA 02154
ATTN: Dr. Ronald McDonald

(1)

Electrochimica
2435 Charleston Road
Mountain View, CA 94040
ATTN: Dr. Eisenberg

(1)

Energy Storage & Conversion Dept.
TRW Systems
One Space Park
Redondo Beach, CA 90278
ATTN: Dr. H.P. Silverman

(1)

Sanders Associates, Inc.
24 Simon Street
Mail Stop NSI-2208
Nashua, NH 03060
ATTN: J. Marshall

(1)

Power Conversion, Inc.
70 MacQuesten Pkwy
Mount Vernon, NY 10550
ATTN: Stuart Chodosh

(1)

Portfolio Manager
Hooker Chemicals & Plastics Corp.
M.P.O. Box 8
Niagara Falls, NY 14302

(1)

G207
S.R.I.
Menlo Park, CA 94025
ATTN: Dr. Leonard Nanis

(1)

Bell Laboratories
600 Mountain Avenue
Murray Hill, NJ 07974
ATTN: Dr. J.J. Auburn, Rm 1A-317

(1)

Jet Propulsion Laboratory
4800 Oak Grove Drive
Pasadena, CA 91103
ATTN: Mr. Harvey Frank
Mail Stop 198-220

(1)

Naval Surface Weapons Center
White Oak Laboratory, Code R-33 (M/S A026)
Silver Spring, MD 20910
ATTN: Dr. D. Ernst

(1)

Energy Conversion Branch Code 3642
Naval Underwater Systems Center
Newport Laboratory
Newport, RI 02840
ATTN: Mr. J. R. Moden

(1)

NASA Lewis Research Center
Mail Stop 6-1
21000 Brookpark Road
Cleveland, OH 44135
ATTN: Dr. Stuart Fordyce (1)

Naval Undersea Center
Code 608
San Diego, CA 92132
ATTN: Mr. Joe McCartney (1)

EIC, Inc.
Newton, MA 02158
ATTN: S.B. Brummer (1)

Altus Corp.
440 Page Mill Road
Palo Alto, CA 94306
ATTN: Douglas Glader (1)

MS 488
NASA Langley Research Center
Hampton, VA 23665
ATTN: J. Bene (1)

Research and Development Division
The Gates Rubber Co.
999 S. Broadway
Denver, CO 80217
ATTN: Mr. Eddie T. Seo (1)

Mail Stop 8C-62
Boeing Aerospace Company
P.O. Box 3999
Seattle, WA 98124
ATTN: Mr. Sidney Gross (1)

Honeywell Technology Center
10701 Lyndale Avenue, South
Bloomington, MN 55420
ATTN: Dr. H.V. Venkatasetty (1)

Jet Propulsion Laboratory
M.S. 198-220
4800 Oak Grove Drive
Pasadena, CA 91103
ATTN: Mr. Aiji Uchiyama (1)

Naval Surface Weapons Center
White Oak Laboratory, Code R-33
Silver Spring, MD 20910
ATTN: Dr. Frank Bis (1)

Dr. Jerry J. Smith
ONR Chemical Program
Arlington, VA 22217 (1)

Saft Corporation of Aermica
711-A Industrial Blvd.
P.O. Box 1284
Valdosta, GA 31601
ATTN: Mr. Lou Adams (1)

Gould Laboratories-Energy Research
40 Gould Center
Rolling Meadows, IL 60008
ATTN: Dr. J. Hall (1)

Electrochem Industries (E-I) Inc.
9990 Wehrle Drive
Clarence, NY 14031
ATTN: Dr. C. Liang (1)

GTE Laboratories Incorporated
40 Sylvan Road
Waltham, MA 02254
ATTN: Dr. C. Schlaiker (1)

Harvey N. Seiger Associates
8 Beacon Hill Drive
Waterford, CT 06385
ATTN: Harvey N. Seiger, Ph.D. (1)

FILMED
2-8