

AD-A120 695


DIFFUSION AND EQUILIBRIUM SWELLING OF MACROMOLECULAR
NETWORKS BY THEIR LINEAR HOMOLOGS(U) AKRON UNIV OH INST
OF POLYMER SCIENCE A N GENT ET AL. OCT 82 TR-20
N00014-76-C-0408






1/1

UNCLASSIFIED

F/G 20/8

NL

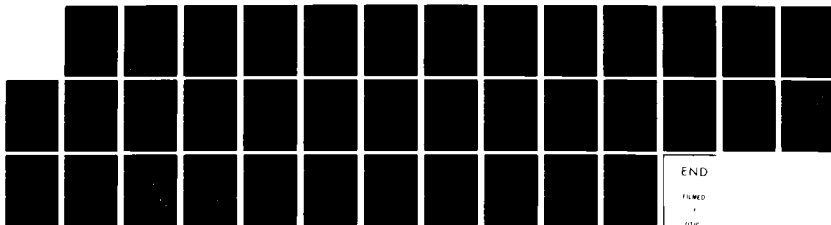



AD A 120695

(12)

OFFICE OF NAVAL RESEARCH

Contract N00014-76-C-0408

Project NR 092-555

Technical Report No. 20 ✓

DIFFUSION AND EQUILIBRIUM SWELLING OF
MACROMOLECULAR NETWORKS BY THEIR LINEAR HOMOLOGS

by

A. N. Gent and R. H. Tobias

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

October, 1982

OCT 22 1982

A

Reproduction in whole or in part is permitted
for any purpose of the United States Government

Approved for Public Release; Distribution Unrestricted

DTIC FILE COPY

82 10 22 002

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 20	2. GOVT ACCESSION NO. AD-A120695	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) DIFFUSION AND EQUILIBRIUM SWELLING OF MACROMOLECULAR NETWORKS BY THEIR LINEAR HOMOLOGS		5. TYPE OF REPORT & PERIOD COVERED Technical Report
7. AUTHOR(s) A. N. Gent and R. H. Tobias		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0408
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE October, 1982
		13. NUMBER OF PAGES 35
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; distribution unrestricted.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted for publication in: Journal of Polymer Science: Polymer Physics Edition		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Absorption, diffusion, molecular networks, polydimethylsiloxane, silicone rubber, swelling equilibrium		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Polydimethylsiloxane (PDMS) networks having strands of molecular weight in the range 11,000-36,000 have been prepared by endlinking linear PDMS molecules of these molecular weights with a tetrafunctional linking agent. Absorption of a series of homologous linear PDMS molecules by the resulting PDMS net- works has been investigated. The diffusion coefficients at 70° were found to be rather large, 1×10^{-12} - 6×10^{-12} m ² /s, and approximately inversely proportional to the molecular weight of		

20. the diffusing liquid, over the range 5,000-38,000. The amount of liquid absorbed at equilibrium was relatively small, 10% - 80%, in good agreement in all cases with an especially simple version of the Flory-Huggins theory when the heat of mixing is made vanishingly small and only entropic terms are retained.

Accession For

NTIS SERIAL

DTIC TAB

Unannounced

Justification

DTIC
COPY
INSPECTED
2

3/N 0102-LF-014-6601

1. Introduction

Little work has been published on the absorption kinetics and equilibrium uptake of polymeric liquids by polymeric hosts. There are several difficulties in carrying out such experiments and in interpreting the results. Most polymer pairs are incompatible, so that the uptake of one polymer by another is extremely small. Also the diffusion of polymeric liquids is generally slow and the diffusion coefficient is itself a function of concentration when the diffusing liquid has a different segmental mobility from the host material. Nevertheless, the results of such experiments should provide a stringent test of the theories both of molecular dynamics (diffusion) and of thermodynamics of mixtures (equilibrium swelling).

A particularly simple system for experiments of this kind is provided by linear macromolecules having reactive endgroups. When the endgroups are linked by tri- or tetra-functional linking agents, a macromolecular network is created. Absorption of further amounts of the linear macromolecules of which this network is composed takes place at a rate dependent upon the diffusion coefficient and to a final extent dependent upon the thermodynamics of mixing.

Certain experimental and theoretical difficulties are absent in this simple system. Because the swelling liquid and the host material are virtually identical, little change

is expected in the effective segmental mobility as the concentration of the diffusant increases. Also, because of the virtual identity of the two components the heat of mixing is expected to be close to zero. Significant amounts of absorption should therefore be obtained even though the swelling liquids are polymers. Indeed, the thermodynamics of swelling equilibrium take a particularly simple form when the heat of mixing is zero. The experimental results should then provide a powerful measure of the entropic contributions to the free energy of swelling for molecular networks in contact with compatible fluids. Moreover, by varying the molecular length of the swelling macromolecules with respect to the length of the molecules comprising the network, the effect of molecular weight upon the diffusion coefficient and upon the equilibrium uptake can be studied.

Difficulties in reaching swelling equilibrium in reasonable times were minimized in the present experiments by employing polydimethylsiloxane fluids and networks for which the glass transition temperature is extremely low, -120°C . Measurements were carried out at an elevated temperature, $+70^{\circ}\text{C}$, i.e., about 200°C above the glass transition temperature, so that the effective segmental mobility was relatively high. The results are presented in the following sections of the paper and compared with the predictions of simple theoretical formulations for the dif-

fusion kinetics and degree of swelling at equilibrium of polymeric networks imbibing linear homologs.

2. Experimental details

a. Preparation of polydimethylsiloxane networks

Linear polydimethylsiloxanes having vinyl endgroups were obtained from Dow Corning Corporation. Three different molecular weight ranges were employed for preparing networks. Vapor phase and membrane osmometry yielded values for $\bar{M}_n$ of 10,000, 24,000, and 37,000 g/g-mole. Endgroup analysis using mercuric acetate (1) gave vinyl contents of 0.47 ± 0.03 , 0.24 ± 0.02 , and 0.15 ± 0.02 percent, corresponding to values for $\bar{M}_n$ of 11,500, 22,500, and 36,000 g/g-mole. GPC data gave $\bar{M}_w/\bar{M}_n$ ratios of approximately 2.0, as reported by Valles and Macosko (2,3) for their similar polymers.

A tetrafunctional silane linking agent, tetrakisdimethylsiloxysilane, was supplied by Prof. Macosko. Gas chromatography, carried out by Prof. Macosko, revealed that it was approximately 89 percent pure. Si-H group analysis (1) gave an average functionality of 3.50, somewhat different from the expected value of 4, indicating that other constituents are present.

The linking agent was mixed with the divinyl polymer, together with about 5 ppm of a Pt catalyst (4). The mixture was then degassed and cast as a thin sheet on a Teflon surface. Measurements were made of the degree of swelling by

benzene after periods of heating at 70°C. As the endlinking process continued, the degree of swelling of the resulting gel decreased. Complete reaction was found to occur after heating for about 3 days at 70°C, as judged by the equilibrium swelling measurements. Test sheets were therefore prepared by heating for 4 days at 70°C to ensure complete reaction.

Networks were prepared in all cases using the amount of endlinking agent necessary to give a minimum degree of swelling by benzene. This amount was 30 - 50 percent greater than the calculated stoichiometric quantity, even after allowance had been made for the reduced functionality of the linking agent. Thus, the junction points were clearly not exclusively tetrafunctional in nature.

b. Characterization of polydimethylsiloxane liquids

Six polydimethylsiloxane liquids were employed as swelling liquids including the three liquids from which networks had been prepared by endlinking. All of the liquids were characterized by end-group titration, yielding values for $\overline{M}_n$ between 4,700 and 38,900, Table 1. Viscosities were determined at 23°C and 70°C by a falling-ball technique using the relation (5)

$$\eta = 2(\rho_s - \rho_l)g a^2/9v$$

where η is the liquid viscosity, ρ_s and ρ_l are the densities of the ball and liquid, 7,800 and 970 kg/m³, respectively,

g is the acceleration due to gravity, a is the ball radius (0.794 mm) and v is the terminal velocity of fall, which ranged from about 0.1 to 10 mm/s. The values obtained for η are given in Table 1 and are plotted in Figure 1 against the number-average molecular weight $\bar{M}_n$, using logarithmic scales for both axes. The results are seen to be consistent with two linear relations in this representation, having slopes of unity at low molecular weights and 3.5 at high molecular weights. This dependence of viscosity upon molecular weight is commonly observed for polymeric fluids (6), and the critical molecular weight M_b at which the transition takes place from one slope to the other has been generally taken as a measure of the molecular length between entanglements in high-molecular-weight liquids. In the present instance M_b is approximately 17,000, Figure 1. When allowance is made for the use of number-average values for molecular weight in the present experiments, this result is in reasonably good agreement with other determinations of M_b for polydimethylsiloxane liquids, ranging from 24,000 to 37,000 (7,8).

The direct proportionality between viscosity and molecular weight at low molecular weights is consistent with the theoretical relationship of Debye and Bueche (9,10)

$$\eta = \rho_l A (\bar{R}^2 / M) n f / 36$$

where A is Avogadro's number, $\bar{R}^2$ is the mean square

distance between the ends of a randomly-coiled macromolecule and $\bar{M}$ is its molecular weight, n is the number of monomer units per molecule and $\bar{f}$ is the frictional resistance to motion per monomer unit. When a value of $5.3 \times 10^{-21} \text{ m}^2/\text{g-mole}$ is assigned to the characteristic ratio $\bar{R}^2/\bar{M}$ (11) the results given in Figure 1 yield values for $\bar{f}$ of $3.0 \times 10^{-11} \text{ N s/m}$ at 23°C and $1.5 \times 10^{-11} \text{ N s/m}$ at 70°C .

c. Measurement of diffusion coefficient $\bar{D}$ and equilibrium swelling ratio Q .

Test specimens of each network were cut from cast sheets in the form of thin plates, about 25 mm square and about 1.5 mm thick. They were immersed in the various liquid polymers at temperatures of 23°C and 70°C . Measurements were made of the weight uptake m_t at intervals of time until an equilibrium value m_∞ was reached. This took several weeks in some instances. In order to ensure that no interlinking with the imbibed polymer or further endlinking of the test sheets took place during long periods of swelling, some sheets were subsequently extracted with benzene, reweighed, and reswollen, in order to verify that all of the imbibed polymeric liquid could be removed and that the process could be accurately repeated.

Representative plots of the weight uptake m_t , relative to the equilibrium value m_∞ , are shown in

Figures 2 and 3, plotted against $t^{1/2}$, where t is the time of immersion of the sample in the swelling liquid. Values of diffusion coefficient D were calculated from the initial linear portions of the experimental relations, i.e., employing the relation for the early stages of diffusion

$$m_t/m_\infty = 4(Dt/\pi l^2)^{1/2} \quad (1)$$

where l is the thickness of the sample (12). The full curves in Figures 2 and 3 were then calculated from the theoretical relations for the entire diffusion process (13):

$$m_t/m_\infty = 1 - \sum_{n=0}^{\infty} \frac{8}{(2n+1)^2 \pi^2} \exp [-D(2n+1)^2 \pi^2 t / l^2] \quad (2)$$

assuming a concentration-independent diffusion coefficient.

Although agreement with the theoretical diffusion equations was found to be excellent in the early stages of diffusion, for weight gains of up to about one-half of the final amount, the experimental results diverged thereafter from the theoretical relations, being more protracted than theory predicts. This slowing down in diffusion in the later stages is tentatively ascribed to thickening of the sample, i.e., an increase in l , as a result of the swelling process itself. An alternate explanation in terms of selective absorption initially of lower molecular weight components of the swelling liquid was shown not to hold. The swelling liquid was extracted from a partially-swollen sample and found by endgroup analysis to have the same value

of number-average molecular weight $\overline{M}_n$ as the liquid in which the sample was immersed. Thus, no significant amount of selective absorption appeared to take place in the present experiments.

The volume swelling ratio Q was obtained directly from the equilibrium weight gain m_∞ , relative to the initial weight m of the sample:

$$Q = 1 + (m_\infty/m).$$

3. Experimental results and discussion

a. Diffusion

Values of the diffusion coefficient D were determined for each combination of polymeric fluid and polymer network, from the initial slopes of plots like those shown in Figures 2 and 3. They are given in Table 2. They are seen to be relatively large, reflecting the low frictional resistance f to segmental motion for PDMS liquids at a temperature some 200°C above their glass transition temperature. The values of D are also seen to fall within a relatively narrow range, considering the rather large range of average molecular weight of the diffusing liquids and of the network strands of the elastomeric solids into which they diffuse. This dependence upon molecular weight is now explored in some detail.

When the molecular weight of the diffusing liquid is equal to that of the network strands of the solid into which

diffuses, then the process closely resembles self-diffusion. The coefficient $\underline{D}$ may then be regarded as a measure of the coefficient $\underline{D'}$ of self-diffusion. Values $\underline{D'}$ were obtained either directly from measurements with polymeric liquid diffusing into a network prepared from the same material by endlinking, or indirectly, by extrapolating the measured diffusion coefficients $\underline{D}$ over a range of network strand lengths to obtain the value when the network strand length and molecular weight was the same as the molecular weight of the diffusant. Values obtained in this way are given in Table 1, and plotted against average molecular weight $\overline{M_n}$ in Figure 4, using logarithmic scales for both axes. In this presentation the results fall on a straight line with a slope of -1, within experimental error, indicating an inverse proportionality between the coefficient of self-diffusion and molecular weight over the entire range of molecular weights employed: 4,700 - 39,000.

Comparison between viscosity $\underline{\eta}$ and coefficient $\underline{D'}$ of self-diffusion.

According to Bueche (10,14), the product $\underline{D'\eta}$ should be independent of molecular weight and temperature (except for direct proportionality to absolute temperature) and given

$$\underline{D'\eta} = (\rho A/36) (\overline{R^2}/M) kT. \quad (3)$$

Employing appropriate values for the terms on the right hand side of equation 3, the product $\underline{D}'\eta$ is predicted to be about $4.1 \times 10^{-13}N$ at $70^{\circ}C$. This value is in reasonably good agreement with that obtained from experimental values of $\underline{D}'$ (Figure 4) and η at low molecular weights (Figure 1), $\underline{D}'\eta = 6.3 \times 10^{-13}N$.

An alternative way of making this comparison is to calculate the segmental friction coefficient $\underline{f}_0$ from the measured diffusion coefficients using the theoretical relation (15)

$$D' = kT/\underline{f}_0 N.$$

The magnitude of $\underline{f}_0$ obtained in this way is about $9.5 \times 10^{-12}Ns/M$, in good agreement with that obtained from viscosity measurements, about $1.45 \times 10^{-11}Ns/m$. These values are also in good agreement with an upper limit of $9 \times 10^{-12}Ns/m$ obtained for linear PDMS liquids at $30^{\circ}C$ by Barlow, Harrison, and Lamb using viscoelastic relaxation measurements (16).

Thus, the measured coefficients of self-diffusion for PDMS materials, determined as described earlier, are in good agreement with independent measurements of viscosity. Both measures suggest that molecular motion in PDMS liquids and networks is largely unrestrained by molecular entanglements up to number-average molecular weights of about 17,000 for η and up to at least twice this value for $\underline{D}'$.

It is particularly noteworthy that the diffusion coefficient $\underline{D}'$ does not appear to depend more strongly on molecular weight at the higher molecular weights. Theoretical considerations of tunnel motion (reptation) suggest that $\underline{D}'$

should be proportional to $\underline{M}^{-2}$ (17). Bueche suggested a proportionality to $\underline{M}^{-3.5}$ for entangled molecules (14). Apparently, tunnel-like restraints or entanglements do not affect self-diffusion over the present range of molecular weights.

c. Diffusion in networks.

Diffusion into a molecular network of PDMS is strongly affected by the molecular weight of the diffusing liquid, as would be expected. Results given in Table 2 show that the diffusion coefficient for a given network increases by a factor of 3 to 4 as the molecular weight of the diffusant is decreased by a factor of about 8.

The molecular weight of the strands comprising the network appears to have a similar, but somewhat smaller, effect. For a given diffusant, the diffusion coefficient increases by 40 - 70 per cent as the strand molecular weight is decreased by a factor of about 3. It is somewhat surprising that tighter networks should allow more rapid diffusion of a given diffusant, in the same way (but to a lesser degree) as a host liquid of decreasing molecular length. Apparently, the more rapid motion of shorter network strands outweighs the restrictive effects of network topology on diffusion past them of a polymeric liquid.

d. Equilibrium swelling

Values of the equilibrium volume swelling ratio Q , calculated from the weight of PDMS liquid taken up at equilibrium, are given in Table 3 for each combination of PDMS network and PDMS swelling liquid. The amount of swelling liquid taken up ranged from 10-20 per cent for the highest molecular weight liquid up to 50-80 per cent for the lowest molecular weight liquid. These values are now compared with the predictions of the Flory-Huggins swelling theory (18), which takes the form:

$$Q^2 \ln(1-Q^{-1}) + Q + \chi + (M_s/M_c)(Q^{5/3} - 2Q/f) = 0 \quad 4.$$

when the densities of the swelling liquid and the polymer network are assumed equal. In this relation, M_s denotes the molecular weight of the swelling liquid, M_c is the network strand molecular weight, f is the functionality of the junction points where the network strands are interconnected and χ is a parameter describing the (unfavorable) heat of interaction between the network polymer and the swelling liquid.

For the present systems, it is certainly true that the densities of the swelling liquid and the polymer network are effectively equal. The functionality f of the endlinking agent was, in principle, 4, but in practice it appeared to be about 3.5 by titration of SiH groups (1). This difference does not greatly affect the predictions of equation 4 and a value of 3.5 has been employed hereafter.

The principal unknown quantities in equation 4 are the interaction parameter χ and the network strand molecular weight M_c . The former might well be assumed to be zero for a swelling liquid that

is virtually identical to the network strands with which it comes into contact. When $\underline{x}$ is given the value zero, and $\underline{M}_s$ is equated to $\underline{M}_c$ then equation 4 predicts that the swelling ratio $\underline{Q}$ will be 1.442, i.e., the weight gain will be about 44 per cent. This is a surprisingly large value, about twice as large as the values observed experimentally when the molecular weight of the swelling liquid was equal to the molecular weight of the network strands. As the results given in Table 3 show, the experimental values under these circumstances ranged from 21 to 27 per cent.

However, it is rather naive to assume that the appropriate value of $\underline{M}_c$ in equation 4 is, indeed, given by the molecular weight of the molecules from which the network was made by endlinking. In fact, the term containing $\underline{M}_c$ reflects the elastic resistance of the network to expansion. A more appropriate value of $\underline{M}_c$ is therefore obtained from the tensile modulus of elasticity (Young's modulus $\underline{E}$) using the relation (18)

$$\underline{E} = 3\rho R T/\underline{M}_c. \quad 5$$

When values of $\underline{M}_c$ were determined for each network in this way, they were found to be considerably smaller than the molecular weights of the precursor molecules, only about one-half as large, due to the additional restraints from molecular entanglements and the $\underline{C}_2$ term in the strain-energy function. The degree of swelling with liquids having a molecular weight of only about one-half of that of the precursor molecules is considerably larger, about 35-48 per cent, Table 3, and thus it is relatively close to the value predicted by equation 4.

A complete comparison is shown in Figure 5 between the predictions of equation 4 for the degree of swelling at equilibrium and the

measured values for each network swollen by each liquid. Values of $\underline{M_c}$ for each network were determined from the elastic modulus $\underline{E}$, using equation 5. The agreement between theory and experiment is reasonably good over the entire range. It is interesting to note that the results are relatively insensitive to the value chosen for the interaction parameter χ , at least for swelling liquids having molecular weights comparable to or greater than those of the network strands.

4. Conclusions

Diffusion of PDMS liquids into PDMS networks is readily observed, even for relatively high molecular weight liquids. The diffusion coefficients are quite large at 70°C, 1 to $6 \times 10^{-12} \text{ m}^2/\text{s}$, and approximately inversely proportional to the molecular weight of the diffusing liquid over the range 5,000 to 38,000 g/g-mole. For the lower molecular weight liquids the diffusion coefficients are in good agreement with values calculated from the flow viscosity of the same liquids, using Bueche's relation between the coefficient of self-diffusion and viscosity, equation 3. Thus, diffusion into networks appears to resemble self-diffusion, especially when the molecular weights of the network strands and of the diffusing liquid are equal. The only anomalous feature observed was the lack of agreement at high molecular weights, above about 17,000, where the flow viscosity followed a different dependence upon molecular weight, reflecting the presence of molecular entanglements, whereas the diffusion coefficient continued to follow an inverse proportionality. It is concluded that the influence of molecular entanglements upon the diffusion of polymeric molecules does not become apparent until a substantially higher molecular weight is reached than in the case of liquid-like flow.

The amount of liquid absorbed at equilibrium was found to range from 10 to 80 per cent, depending upon the molecular weight of the diffusing liquid relative to the network strand molecular weight. When the Flory-Huggins theory of swelling equilibrium for polymer networks is specialized to the case of a swelling liquid having the same density as the network material, and with

zero heat of interaction, then it is found to be in reasonably good agreement with the experimental measurements of the amount of absorbed liquid. Thus, the swelling of polymeric networks by homologous polymeric liquids appears to be in good agreement with a simple version of the thermodynamics of swelling equilibrium. However, it should be noted that the theoretical results are relatively insensitive to the value chosen for the heat of interaction over virtually the entire range of values that characterize swelling liquids. Instead, they are strongly dependent upon, and dominated by, the elastic resistance of the network to isotropic expansion.

References

1. R. C. Smith, N. C. Angelotti, and C. L. Hanson, Chap. 7 in "Analysis of Silicones," A. L. Smith, ed., John Wiley and Sons, New York, 1974.
2. E. M. Valles and C. W. Macosko, Rubber Chem. Technol. 49, 1232 (1976).
3. E. M. Valles and C. W. Macosko, Macromolecules 13, 521 (1979).
4. C. B. Kauffman and D. O. Cowan, Chap. VIII in "Inorganic Synthesis," Vol. 6, E. G. Rochow, ed., McGraw-Hill, New York, 1969.
5. H. Lamb, "Hydrodynamics," 6th ed., Cambridge University Press, London, 1932, reprinted, Dover, New York, 1945, Art. 337, pp. 597-602.
6. T. G. Fox and S. Loshaek, J. Appl. Phys. 26, 1080 (1955).
7. G. C. Berry and T. G. Fox, Adv. Polym. Sci. 5, 261 (1968).
8. T. Kataoka and S. Ueda, J. Polymer Sci. A-2, 5, 973 (1967).
9. P. Debye, J. Chem. Phys. 14, 636 (1946).
10. F. Bueche, J. Chem. Phys. 20, 1959 (1952).
11. P. J. Flory, "Principles of Polymer Chemistry," Cornell University Press, Ithaca, New York, 1953.
12. J. Crank and G. S. Park, Chap. 1 in "Diffusion in Polymers," J. Crank and G. S. Park, ed., Academic Press, London, 1968.
13. J. Crank, "Mathematics of Diffusion," 2nd ed., Clarendon Press, Oxford, 1975.
14. F. Bueche, "Physical Properties of Polymers," John Wiley and Sons, New York, 1962, pp. 70-72.

15. A. Einstein, Ann. Physik 17, 549 (1905).
16. A. J. Barlow, G. Harrison, and J. Lamb, Proc. Roy. Soc. (London) A282, 228 (1964).
17. P. G. de Gennes, "Scaling Concepts in Polymer Physics,"
Cornell University Press, New York, 1979.
18. L. R. G. Treloar, "The Physics of Rubber Elasticity," 3rd ed.,
Clarendon Press, Oxford, 1975.

Table 1. Number-average molecular weight $\overline{M}_n$, viscosity η and coefficient $\underline{D}$ of self-diffusion for polydimethylsiloxane liquids.

$\overline{M}_n$ (g/g-mole)	η at 23°C (N s/m ²)	η at 70°C (N s/m ²)	$\underline{D} \times 10^{12}$ at 70°C (m ² /s)
4,700	0.15	0.075	6.3 ± 1.0^a
11,500	0.46	0.20	3.5 ± 0.5
22,500	2.5	1.15	1.75 ± 0.25^a
24,900	2.6	1.20	1.25 ± 0.25
36,000	9.0	4.2	1.25 ± 0.18
38,900	9.4	4.45	0.95 ± 0.2^a

^a obtained by extrapolation from $\underline{D}$ vs $\overline{M}_n$ of network.

Table 2. Diffusion coefficient $\underline{D}$ ($\text{m}^2/\text{s} \times 10^{12}$), calculated from equation 1, for PDMS liquids diffusing into PDMS networks.

Molecular weight

$\underline{M}_n$ of diffusant (g/g-mole) Network strand molecular weight $\underline{M}_c$ (g/g-mole)
Measurements at 70°C

	11,500	22,500	36,000
4,700	4.91 ± 0.65	4.49 ± 0.60	3.63 ± 0.49
11,500	3.52 ± 0.48	3.74 ± 0.52	2.43 ± 0.34
22,500	1.71 ± 0.24	1.75 ± 0.25	1.33 ± 0.19
24,900	1.58 ± 0.23	1.38 ± 0.21	1.02 ± 0.15
36,000	1.89 ± 0.27	1.67 ± 0.24	1.26 ± 0.18
38,900	1.72 ± 0.25	1.34 ± 0.20	0.98 ± 0.15

Measurements at 23°C

4,700	---	---	1.63 ± 0.23
11,500	---	---	0.99 ± 0.15

Table 3. Equilibrium volume swelling ratio Q for PDMS
networks swollen by PDMS liquids at 70°C.

Molecular weight

$\bar{M}_n$ of liquid (g/g-mole)	Network strand molecular weight $\bar{M}_c$ (g/g-mole)		
	11,500	22,500	36,000
4,700	1.477	1.610	1.773
11,500	1.271	1.375	1.572
22,500	1.149	1.220	1.283
24,900	1.151	1.219	1.287
36,000	1.109	1.162	1.211
38,900	1.111	1.165	1.213

Figure Legends

- Figure 1. Flow viscosity η of PDMS liquids vs number-average molecular weight $\bar{M}_n$.
- Figure 2. Weight uptake m_t of PDMS liquid ($\bar{M}_n = 4,700$ g/g-mole), relative to the equilibrium value m_∞ , vs $t^{1/2}/l$, where t is the time of immersion in the swelling liquid and l is the thickness of the sample, a thin sheet of an end-linked PDMS network having $M_c = 11,500$ g/g-mole. Full curve calculated from equation 2.
- Figure 3. Weight uptake m_t of PDMS liquid ($\bar{M}_n = 11,500$ g/g-mole), relative to the equilibrium value m_∞ , vs $t^{1/2}/l$, where t is the time of immersion in the swelling liquid and l is the thickness of the sample, a thin sheet of an end-linked PDMS network having $M_c = 36,000$. Full curve, calculated from equation 2.
- Figure 4. Coefficient D' of self-diffusion of PDMS liquids vs number-average molecular weight $\bar{M}_n$. Filled-in circles, measured directly; open circles, obtained by extrapolation as described in the text.
- Figure 5. Equilibrium volume swelling ratio Q vs the ratio M_s/M_c of the molecular weight of the swelling liquid to that of the network strands. M_c was obtained from measurements of Young's modulus E , using equation 5. Full curve, calculated from equation 4 with $\chi = 0$; broken curve, with $\chi = 0.25$; dotted curve, with $\chi = 0.5$.

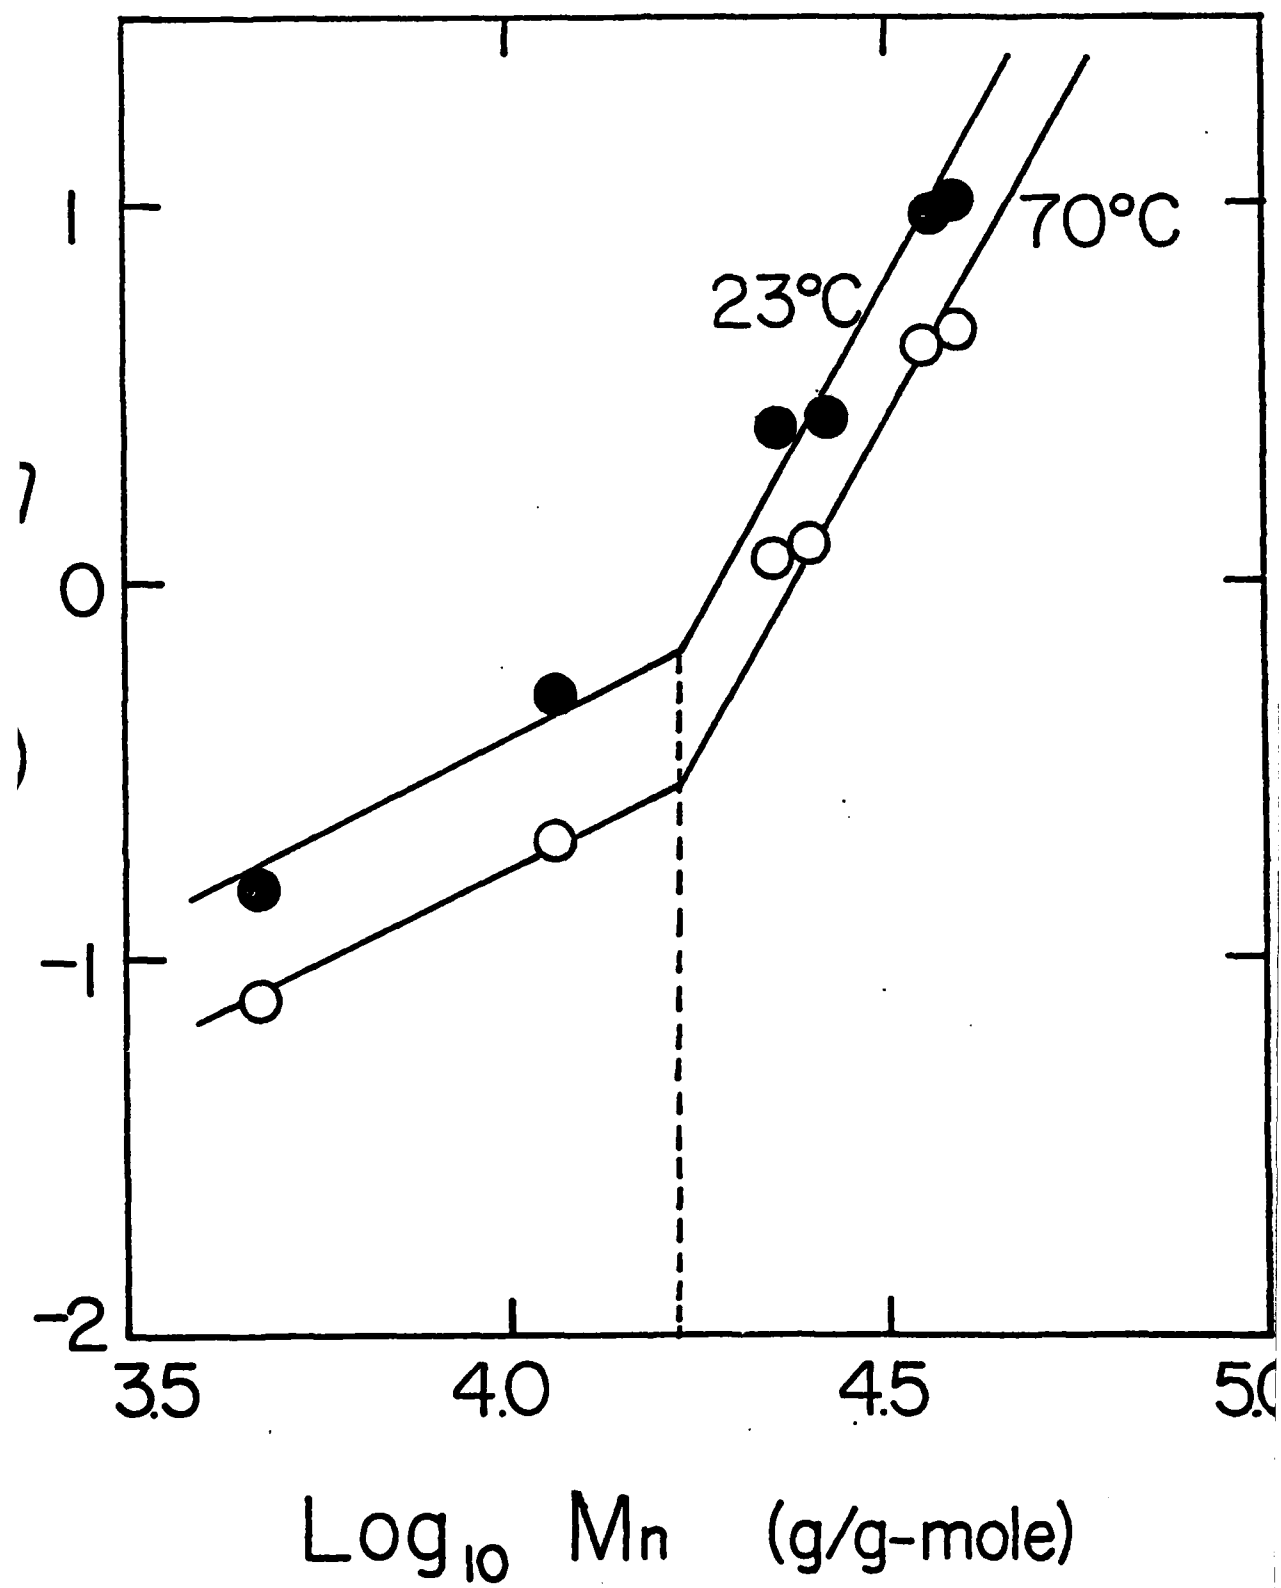


FIGURE 1

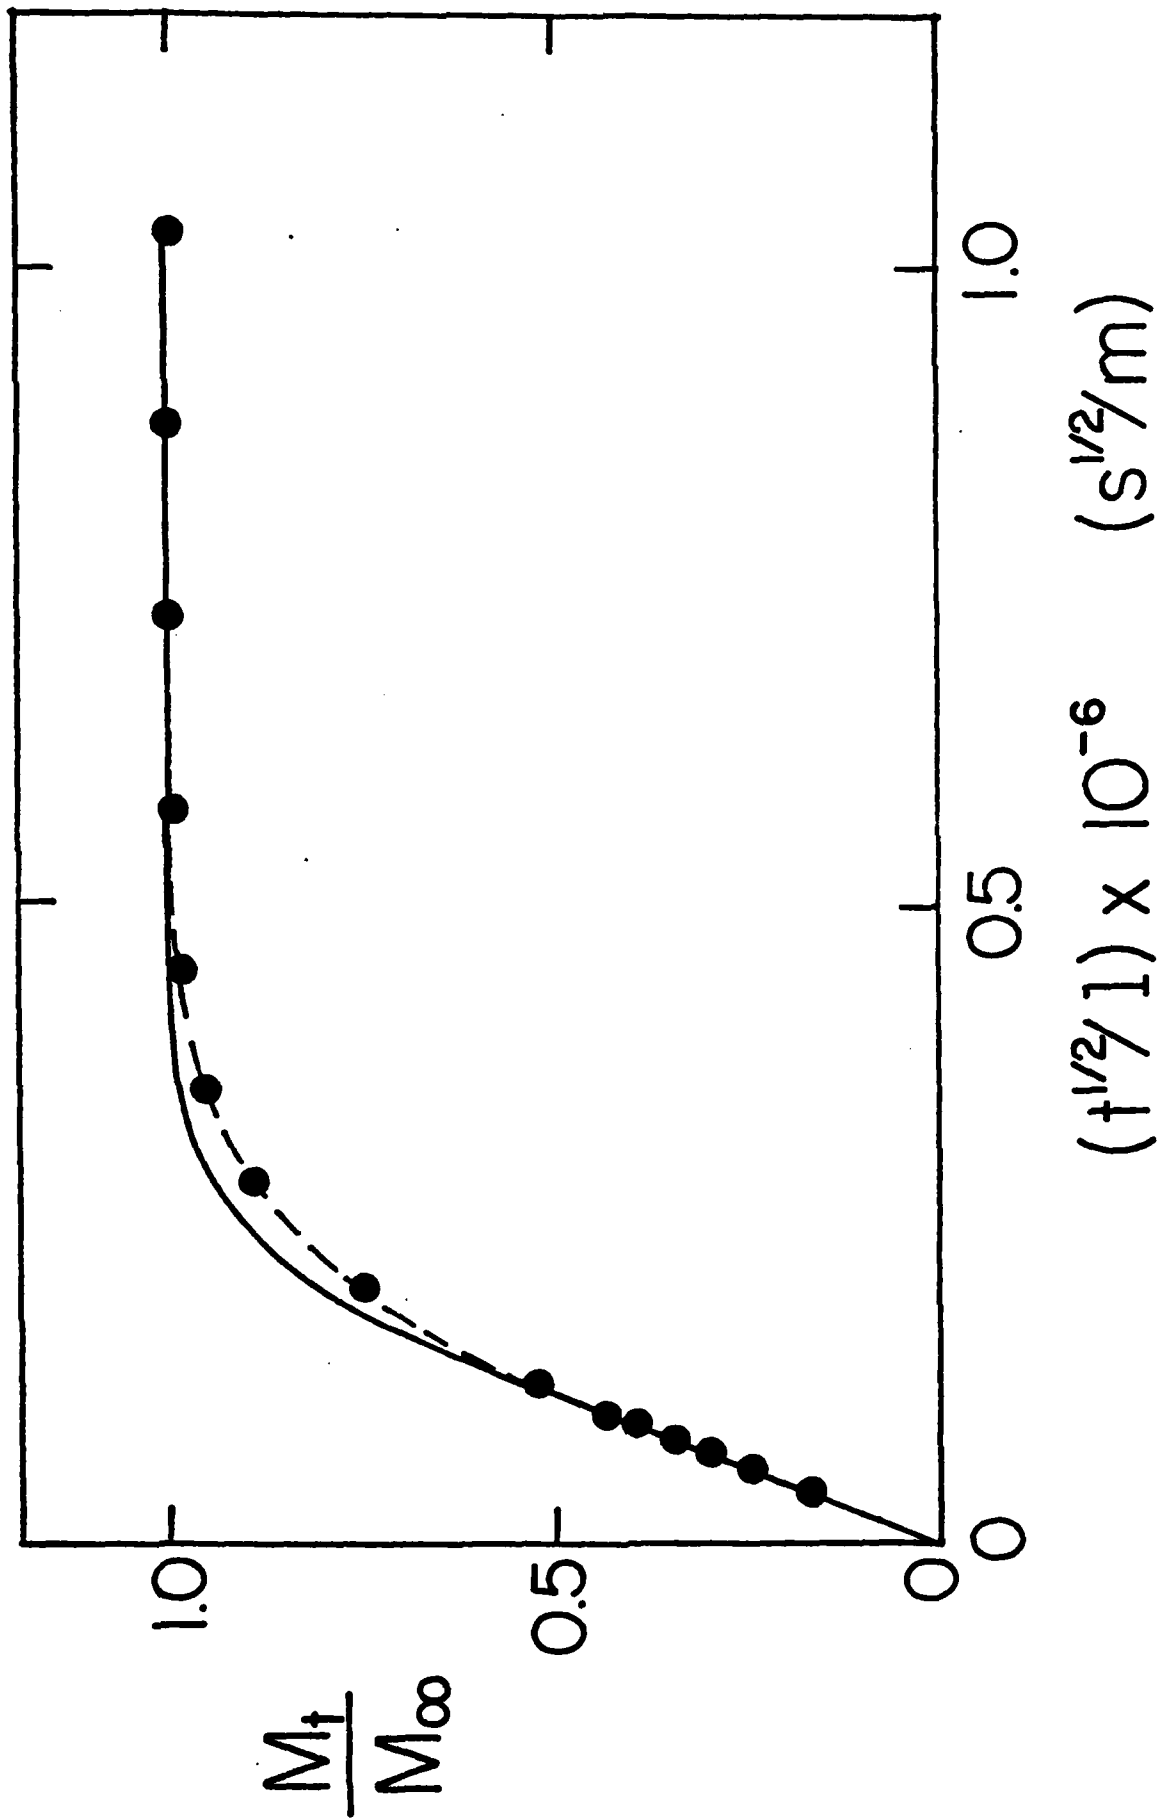


FIGURE 2

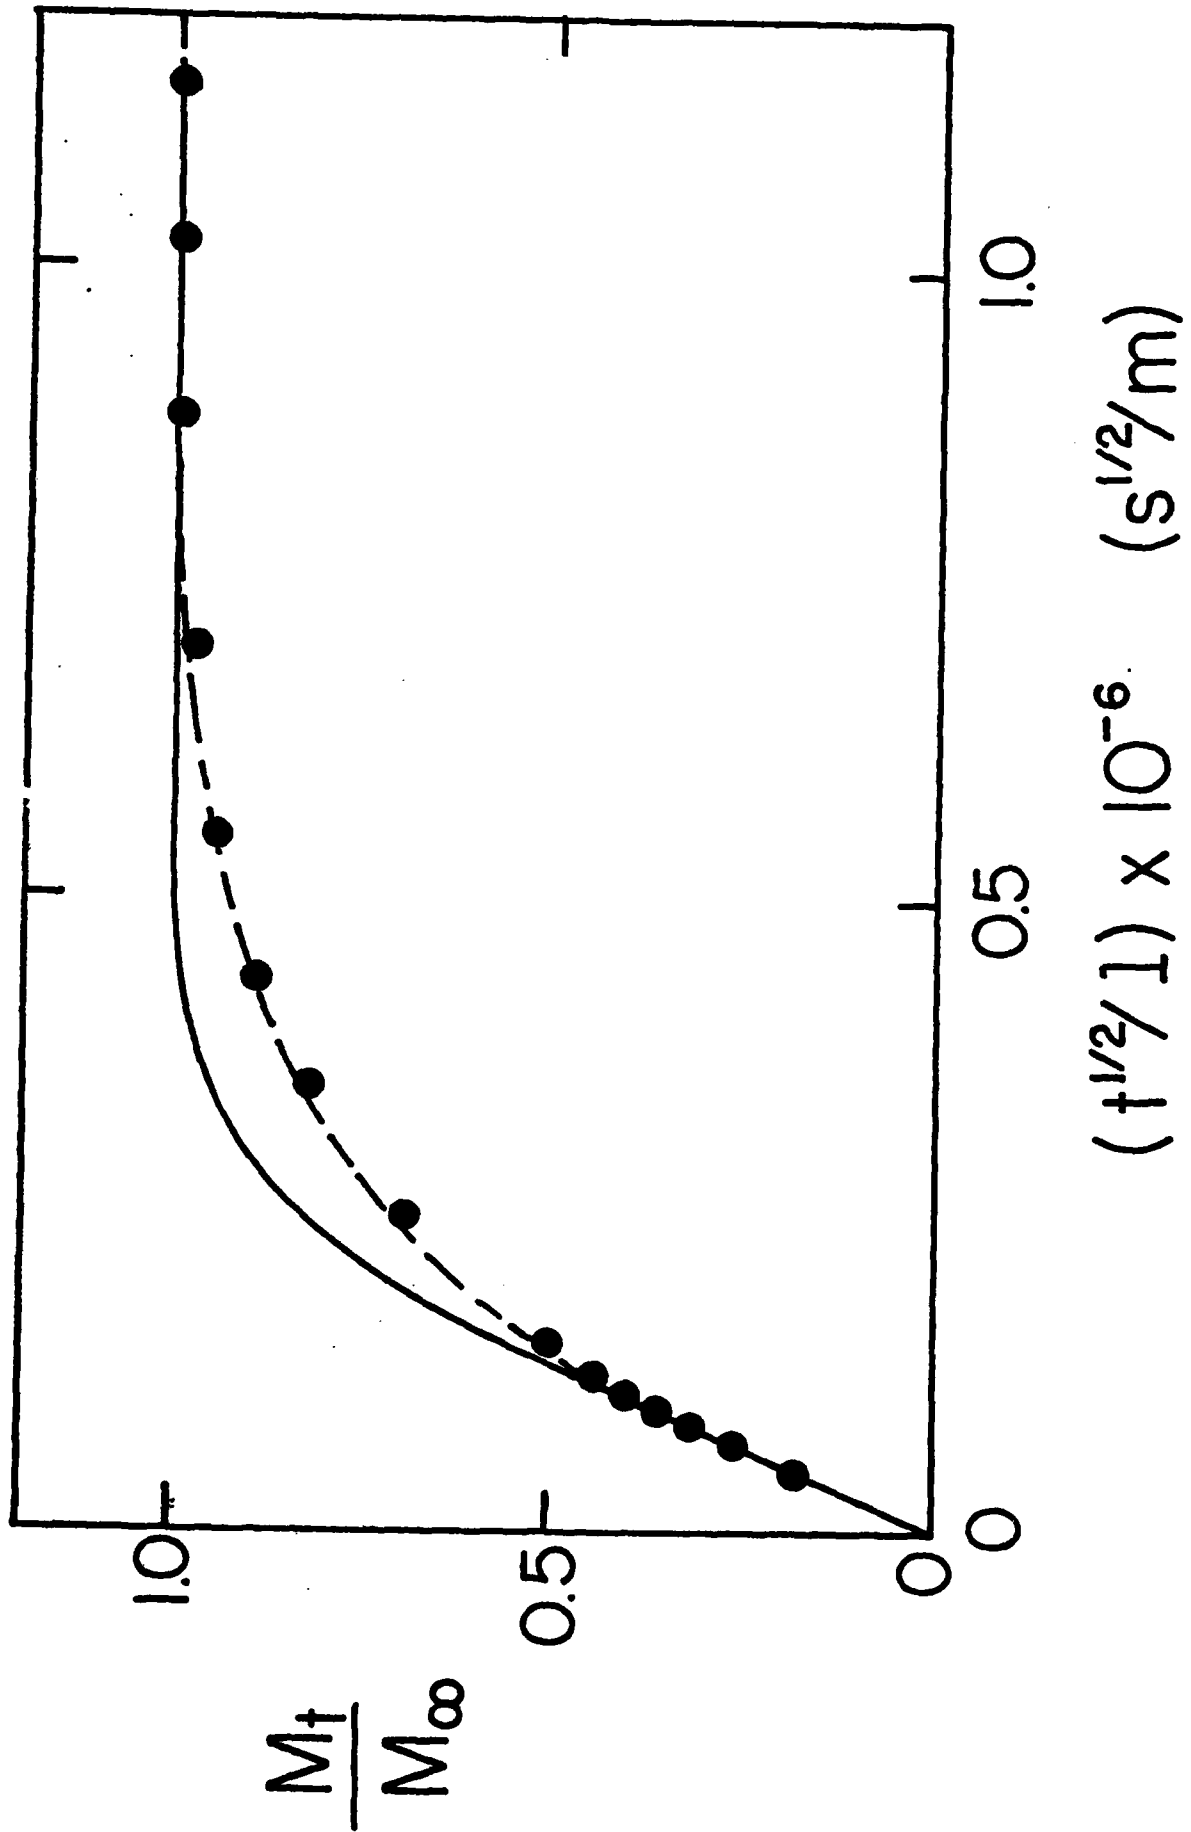


FIGURE 3

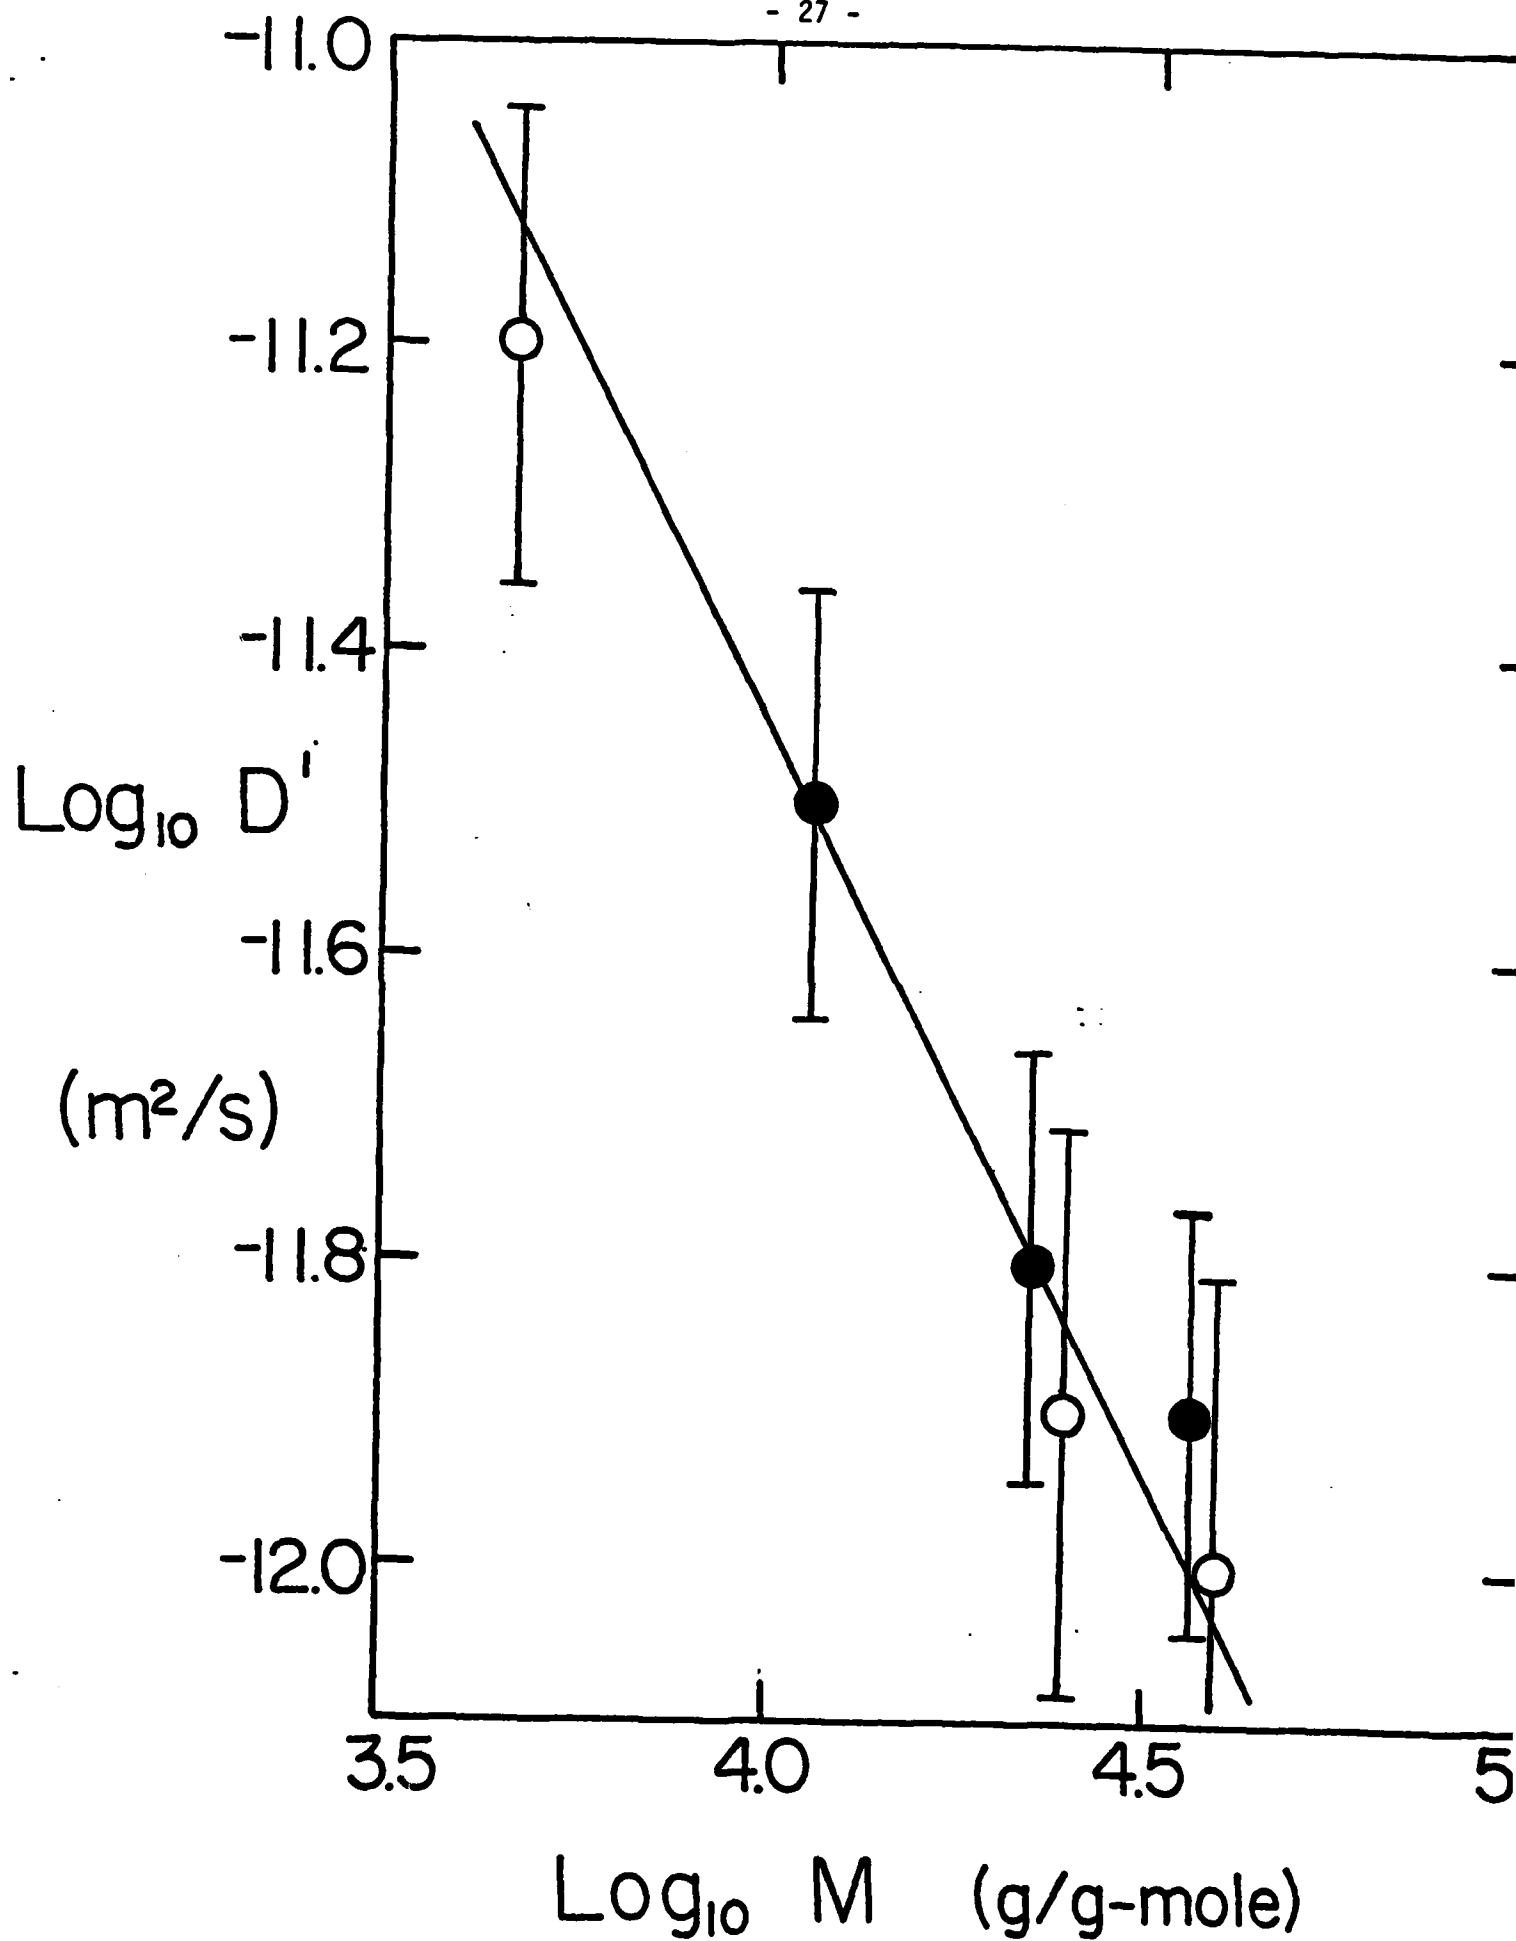


FIGURE 4

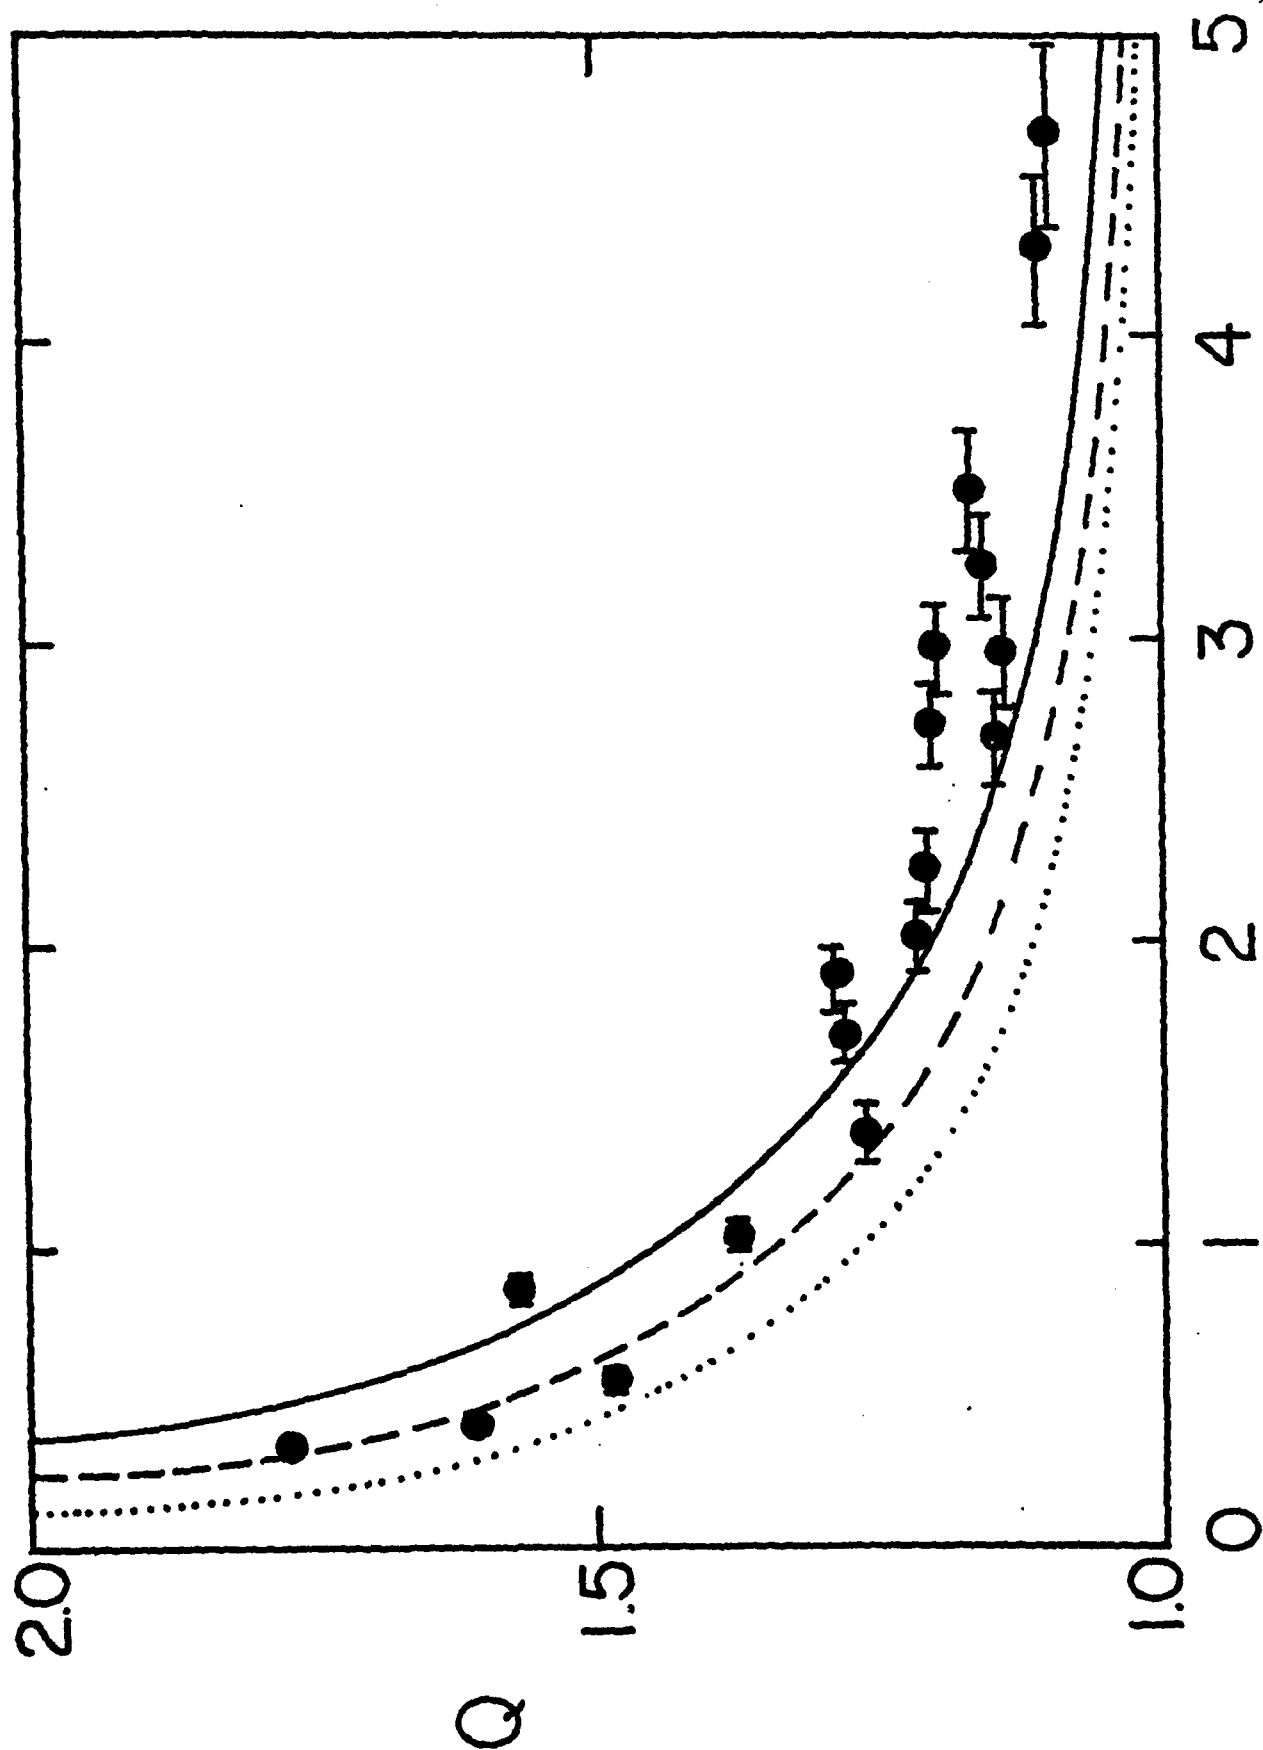


FIGURE 5
 M_c/M_{c0}

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. L.V. Schmidt Assistant Secretary of the Navy (R,E, and S) Room 5E 731 Pentagon Washington, D.C. 20350	1	Dr. F. Roberto Code AFRPL MKPA Edwards AFB, CA 93523	1
Dr. A.L. Slafkosky Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1	Dr. L.H. Caveny Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, D.C. 20332	1
Dr. Richard S. Miller Office of Naval Research Code 413 Arlington, VA 22217	10	Mr. Donald L. Ball Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, D.C. 20332	1
Mr. David Siegel Office of Naval Research Code 260 Arlington, VA 22217	1	Dr. John S. Wilkes, Jr. FJSRL/NC USAF Academy, CO 80840	1
Dr. R.J. Marcus Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106	1	Dr. R.L. Lou Aerojet Strategic Propulsion Co. P.O. Box 15699C Sacramento, CA 95813	1
Dr. Larry Peebles Office of Naval Research East Central Regional Office 666 Summer Street, Bldg. 114-D Boston, MA 02210	1	Dr. V.J. Keenan Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301	1
Dr. Phillip A. Miller Office of Naval Research San Francisco Area Office One Hallidie Plaza, Suite 601 San Francisco, CA 94102	1	Dr. Philip Howe Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD 21005	1
Mr. Otto K. Heiney AFATL - DLDL Elgin AFB, FL 32542	1	Mr. L.A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1
Mr. R. Geisler ATTN: MKP/MS24 AFRPL Edwards AFB, CA 93523	1	Dr. W.W. Wharton Attn: DRS/II-RXL Commander U.S. Army Missile Command Redstone Arsenal, AL 35898	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. R.G. Rhoades Commander Army Missile Command DRSMI-R Redstone Arsenal, AL 35898	1	Dr. E.H. Debutts Hercules Inc. Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. W.D. Stephens Atlantic Research Corp. Pine Ridge Plant 7511 Wellington Rd. Gainesville, VA 22065	1	Dr. James H. Thacher Hercules Inc. Magna Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. A.W. Barrows Ballistic Research Laboratory USA ARRADCOM DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Mr. Theodore M. Gilliland Johns Hopkins University APL Chemical Propulsion Info. Agency Johns Hopkins Road Laurel, MD 20810	1
Dr. C.M. Frey Chemical Systems Division P.O. Box 358 Sunnyvale, CA 94086	1	Dr. R. McGuire Lawrence Livermore Laboratory University of California Code L-324 Livermore, CA 94550	1
Professor F. Rodriguez Cornell University School of Chemical Engineering Olin Hall, Ithaca, N.Y. 14853	1	Dr. Jack Linsk Lockheed Missiles & Space Co. P.O. Box 504 Code Org. 83-10, Bldg. 154 Sunnyvale, CA 94088	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Dr. B.G. Craig Los Alamos National Lab P.O. Box 1663 NSP/DOD, MS-245 Los Alamos, NM 87545	1
Dr. Rocco C. Musso Hercules Aerospace Division Hercules Incorporated Alleghany Ballistic Lab P.O. Box 210 Washington, D.C. 21502	1	Dr. R.L. Rabie WX-2, MS-952 Los Alamos National Lab. P.O. Box 1663 Los Alamos NM 37545	1
Dr. Ronald L. Simmons Hercules Inc. Eglin AFATL/DL DL Eglin AFB, FL 32542	1	Dr. R. Rogers Los Alamos Scientific Lab. P.O. Box 1663 Los Alamos, NM 87545	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. R. Brown Naval Air Systems Command Code 330 Washington, D.C. 20361	1	Dr. J. Schnur Naval Research Lab. Code 6510 Washington, D.C. 20375	1
Dr. H. Rosenwasser Naval Air Systems Command AIR-310C Washington, D.C. 20360	1	Mr. R. Beauregard Naval Sea Systems Command SEA 64E Washington, D.C. 20362	1
Mr. B. Sobers Naval Air Systems Command Code 03P25 Washington, D.C. 20360	1	Mr. G. Edwards Naval Sea Systems Command Code 62R3 Washington, D.C. 20362	1
Dr. L.R. Rothstein Assistant Director Naval Explosives Dev. Engineering Dept. Naval Weapons Station Yorktown, VA 23691	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, PA 19112	1
Dr. Lionel Dickinson Naval Explosive Ordnance Disposal Tech. Center Code D Indian Head, MD 20640	1	Dr. H.G. Adolph Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1
Mr. C.L. Adams Naval Ordnance Station Code PM4 Indian Head, MD 20640	1	Dr. T.D. Austin Naval Surface Weapons Center Code R16 Indian Head, MD 20640	1
Mr. S. Mitchell Naval Ordnance Station Code 5253 Indian Head, MD 20640	1	Dr. T. Hall Code R-11 Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910	1
Dr. William Tolles Dean of Research Naval Postgraduate School Monterey, CA 93940	1	Mr. G.L. Mackenzie Naval Surface Weapons Center Code R101 Indian Head, MD 20640	1
Naval Research Lab. Code 6100 Washington, D.C. 20375	1	Dr. K.F. Mueller Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. J. Murrin Naval Sea Systems Command Code 62R2 Washington, D.C. 20362	1	Dr. A. Nielsen Naval Weapons Center Code 385 China Lake, CA 93555	1
Dr. D.J. Pastine Naval Surface Weapons Center Code R04 White Oak Silver Spring, MD 20910	1	Dr. R. Reed, Jr. Naval Weapons Center Code 388 China Lake, CA 93555	1
Mr. L. Roslund Naval Surface Weapons Center Code R122 White Oak, Silver Spring MD 20910	1	Dr. L. Smith Naval Weapons Center Code 3205 China Lake, CA 93555	1
Mr. M. Stosz Naval Surface Weapons Center Code R121 White Oak Silver Spring, MD 20910	1	Dr. B. Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1
Dr. E. Zimmet Naval Surface Weapons Center Code R13 White Oak Silver Spring, MD 20910	1	Dr. A. Faulstich Chief of Naval Technology MAT Code 0716 Washington, D.C. 20360	1
Dr. D. R. Derr Naval Weapons Center Code 388 China Lake, CA 93555	1	LCDR J. Walker Chief of Naval Material Office of Naval Technology MAT, Code 0712 Washington, D.C. 20360	1
Mr. Lee N. Gilbert Naval Weapons Center Code 3205 China Lake, CA 93555	1	Mr. Joe McCartney Naval Ocean Systems Center San Diego, CA 92152	1
Dr. E. Martin Naval Weapons Center Code 3858 China Lake, CA 93555	1	Dr. S. Yamamoto Marine Sciences Division Naval Ocean Systems Center San Diego, CA 91232	1
Mr. R. McCarten Naval Weapons Center Code 3272 China Lake, CA 93555	1	Dr. G. Bosmajian Applied Chemistry Division Naval Ship Research & Development Center Annapolis, MD 21401	1
		Dr. H. Shuey Rohn and Haas Company Huntsville, Alabama 35801	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. J.F. Kincaid Strategic Systems Project Office Department of the Navy Room 901 Washington, D.C. 20376	1	Dr. C.W. Vriesen Thiokol Elkton Division P.O. Box 241 Elkton, MD 21921	1
Strategic Systems Project Office Propulsion Unit Code SP2731 Department of the Navy Washington, D.C. 20376	1	Dr. J.C. Hinshaw Thiokol Wasatch Division P.O. Box 524 Brigham City, Utah 84302	1
Mr. E.L. Throckmorton Strategic Systems Project Office Department of the Navy Room 1048 Washington, D.C. 20376	1	U.S. Army Research Office Chemical & Biological Sciences Division P.O. Box 12211 Research Triangle Park NC 27709	1
Dr. D.A. Flanigan Thiokol Huntsville Division Huntsville, Alabama 35807	1	Dr. R.F. Walker USA ARADCOM ORDAR-LCE Dover, NJ 07801	1
Mr. G.F. Mangum Thiokol Corporation Huntsville Division Huntsville, Alabama 35807	1	Dr. T. Sinden Munitions Directorate Propellants and Explosives Defence Equipment Staff British Embassy 3100 Massachusetts Ave. Washington, D.C. 20008	1
Mr. E.S. Sutton Thiokol Corporation Elkton Division P.O. Box 241 Elkton, MD 21921	1	LTC B. Loving AFROL/LK Edwards AFB, CA 93523	1
Dr. G. Thompson Thiokol Wasatch Division MS 240 P.O. Box 524 Brigham City, UT 84302	1	Professor Alan N. Gent Institute of Polymer Science University of Akron Akron, OH 44325	1
Dr. T.F. Davidson Technical Director Thiokol Corporation Government Systems Group P.O. Box 9258 Ogden, Utah 84409	1	Mr. J. M. Frankle Army Ballistic Research Labs ARADCOM Code ORDAR-BLI Aberdeen Proving Ground, MD 21005	1

DISTRIBUTION LIST

<u>No. Copies</u>	<u>No. Copies</u>
Dr. Ingo W. May Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005 1	Dr. J. P. Marshall Dept. 52-35, Bldg. 204/2 Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304 1
Professor N.W. Tschoegl California Institute of Tech Dept. of Chemical Engineering Pasadena, CA 91125 1	Ms. Joan L. Janney Los Alamos National Lab Mail Stop 920 Los Alamos, NM 87545 1
Professor M.D. Nicol University of California Dept. of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024 1	Dr. J. M. Walsh Los Alamos Scientific Lab Los Alamos, NM 87545 1
Professor A. G. Evans University of California Berkeley, CA 94720 1	Professor R. W. Armstrong Univ. of Maryland Department of Mechanical Eng. College Park, MD 20742 1
Professor T. Litovitz Catholic Univ. of America Physics Department 520 Michigan Ave., N.E. Washington, D.C. 20017 1	Prof. Richard A. Reinhardt Naval Postgraduate School Physics & Chemistry Dept. Monterey, CA 93940 1
Professor W. G. Knauss Graduate Aeronautical Lab California Institute of Tech. Pasadena, CA 91125 1	Dr. R. Bernecker Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910 1
Professor Edward Price Georgia Institute of Tech. School of Aerospace Engin. Atlanta, Georgia 30332 1	Dr. M. J. Kamlet Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910 1
Dr. Kenneth O. Hartman Hercules Aerospace Division Hercules Incorporated P.O. Box 210 Cumberland, MD 21502 1	Professor J. D. Achenbach Northwestern University Dept. of Civil Engineering Evanston, IL 60201 1
Dr. Thor L. Smith IBM Research Lab D42.282 San Jose, CA 95193 1	Dr. N. L. Basdekas Office of Naval Research Mechanics Program, Code 432 Arlington, VA 22217 1
	Professor Kenneth Kuo Pennsylvania State Univ. Dept. of Mechanical Engineering University Park, PA 16802 1

DISTRIBUTION LIST

	<u>No. Copies</u>	<u>No. Copies</u>
Dr. S. Sheffield Sandia Laboratories Division 2513 P.O. Box 5800 Albuquerque, NM 87185	1	
Dr. M. Farber Space Sciences, Inc. 135 Maple Avenue Monrovia, CA 91016	1	
Dr. Y. M. Gupta SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Mr. M. Hill SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Professor Richard A. Schapery Texas A&M Univ. Dept of Civil Engineering College Station, TX 77843	1	
Dr. Stephen Swanson Univ. of Utah Dept. of Mech. & Industrial Engineering MEB 3008 Salt Lake City, UT 84112	1	
Mr. J. D. Byrd Thiokol Corp. Huntsville Huntsville Div. Huntsville, AL 35807	1	
Professor G. D. Duvall Washington State University Dept. of Physics Pullman, WA 99163	1	
Prof. T. Dickinson Washington State University Dept. of Physics Pullman, WA 99163	1	

END

FILMED