

AD A127006

(12)

(8)

OFFICE OF NAVAL RESEARCH

Contract N00014-76-C-0408

Project NR 092-555

Technical Report No. 27 ✓

TEAR STRENGTH OF ELASTOMERS UNDER THRESHOLD CONDITIONS

by

A. K. Bhowmick, A. N. Gent and C. T. R. Pulford

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

April, 1983

DTIC
ELECTE
S APR 18 1983 D
B

Reproduction in whole or in part is permitted
for any purpose of the United States Government

Approved for Public Release; Distribution Unrestricted

DTIC FILE COPY

83 04 18 101

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 27	2. GOVT ACCESSION NO. AD-A127 006	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Tear Strength of Elastomers under Threshold Conditions		5. TYPE OF REPORT & PERIOD COVERED Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) A. K. Bhowmick, A. N. Gent and C. T. R. Pulford		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0408
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, VA 22217		12. REPORT DATE April, 1983
		13. NUMBER OF PAGES 24
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; distribution unrestricted.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted for publication in: Rubber Chemistry and Technology		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Crack propagation, Crosslinking, Elastomers, Fracture, Reinforcement, Rubber, Strength, Tear resistance.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) → Measurements have been made of the tear strength of several elastomeric materials under threshold conditions, i.e., in the swollen state and at high temperatures when dissipative contributions to the work of fracture are minimized. The materials studied were Neoprene WRT, PB, SBR, EPDM and a castable polysulfide material, LP-32. They were crosslinked to different degrees, using a free-radical source, or sulfur, or a metal oxide as the crosslinking reagent. Values obtained for the threshold tear strength →		

DD FORM 1473

1 JAN 73

EDITION OF 1 NOV 65 IS OBSOLETE

S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. (continued)

→ were similar in all cases, lying in the range 50 - 200 J/m². They appeared to be approximately proportional to $E^{-1/2}$, where E is the tensile (Young's) modulus of the elastomer, as predicted by the theoretical treatment of Lake and Thomas. Values for networks with polysulfidic crosslinks were significantly higher than with monosulfide or C-C crosslinks, by about a factor of 2. Values for carbon-black-filled materials were higher also, by about the same factor, in comparison with the equivalent unfilled materials. These effects are attributed to rupture of labile crosslinks, or bonds to carbon black, prior to main-chain rupture. ←

Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By _____	
Distribution/	
Availability	
Dist	Avail and/or Special
A	



S/N 0102- LP 014-6601

Introduction

The tear strength or fracture energy of a material, denoted here G_c , represents the amount of mechanical energy required to propagate a tear through a unit area of the material. Vulcanized rubber compounds have a minimum tear strength under certain conditions, when visco-elastic and other dissipative processes are minimized. This minimum strength, denoted here the threshold strength, has been measured previously for a number of elastomeric networks (1-4). The results have been found to agree satisfactorily with a theoretical treatment due to Lake and Thomas (5) both in absolute magnitude and in the dependence upon the degree of crosslinking (3,4). In accordance with the theory, the threshold tear strength is found to increase with increasing length of the molecular strands comprising the network, approximately in proportion to $M_c^{\frac{1}{2}}$ where M_c is the average molecular weight of a network strand. Thus, the relationship for the threshold tear strength G_{co} is

$$G_{co} = K M_c^{\frac{1}{2}}. \quad (1)$$

The coefficient K relating the threshold tear strength to the molecular weight of network strands is itself dependent upon the chemical structure of the molecules comprising the network. It depends upon the length of the main-chain bonds, the average mass per main-chain atom, the flexibility of the chain and the dissociation energy of the weakest main-chain bond. This dependence has been shown to account for the particularly low threshold strengths of silicone rubber and phosphonitrilic fluoroelastomer compared to polybutadiene and polyisoprene (3,4). The principal factor responsible is

the larger average mass per main-chain atom for the former two elastomers compared to the latter.

Equation 1 can be reformulated in terms of the tensile (Young's) modulus E of elasticity of the material, using the theoretical relation (6)

$$M_c = 3\rho RT/E$$

where R is the gas constant and T is absolute temperature. Equation 1 then becomes

$$G_{co} = K_1 E^{-1/2}, \quad (2)$$

and predicts that the threshold tear strength is a slowly decreasing function of Young's modulus E .

Measurements have now been made of the threshold tear strengths for several other elastomeric materials: a representative copolymer of styrene and butadiene (25:75, SBR 1502, Firestone Tire and Rubber Company; polychloroprene (Neoprene WRT, E. I. Du Pont de Nemours & Co.); a polysulfide sealant material (Thiokol LP-32); and a copolymer of ethylene and propylene (EPDM, Vistalon 4608, Exxon Chemical Company). These materials represent a wide variety of chemical structures.

In addition, measurements have been made of the threshold strength of molecular networks prepared by free-radical crosslinking, when the molecules are interlinked by C-C bonds, and by sulphur crosslinking systems of various kinds, in order to study the effect of crosslink type upon the threshold tear strength.

Finally, some preliminary measurements are reported of the threshold fracture energies for a carbon-black-reinforced elastomer.

Experimental

(a) Preparation of test strips

Mix formulations and vulcanization conditions are given in Table 1. In all cases, vulcanized rubber sheets were prepared, about 1 - 2 mm thick. Test strips were then cut from the sheets, about 2 cm wide and 6 cm long.

(b) Measurement of tear strength

The threshold tear strength is attained when dissipative processes are minimized. Measurements of the tear strength were therefore carried out at high temperatures, 80°C - 150°C, at low rates of tearing, 1 - 10 $\mu\text{m/s}$, and using samples swollen with mobile liquids. Test strips were scored along a central line to a depth of about one-half of the thickness, leaving the other half to be torn through, as shown schematically in Figure 1. The tear strength G_c was calculated from the tear force F as follows

$$G_c = 2 \lambda_s^2 F/w$$

where λ_s is the linear swelling ratio of the sample and w is the measured width of the tear path (Figure 1b). The factor λ_s^2 takes into account the reduced number of network strands crossing a unit area in the swollen material. For unswollen specimens $\lambda_s = 1$.

Polybutadiene (PB), SBR and EPDM materials were swollen with liquid paraffin oil. Neoprene WRT and Thiokol LP-32 vulcanizates were swollen with 1, 2, 4-trichlorobenzene (TCB).

(c) Measurement of E

Values of E were determined from tensile stress-strain relations at small strains, using unswollen samples.

Results and discussion

Experimentally-determined values of the threshold tear strength G_{CO} are given in Table 2 for all of the materials examined. They show several important features, as discussed below.

Polychloroprene materials

It proved possible to crosslink the polychloroprene elastomer with either an oxide crosslinking system or a sulfur crosslinking system, although in neither case was it found possible to obtain a high degree of crosslinking. Values of Young's modulus E were consequently rather low, Table 2. When conventional formulations were used, capable of forming both types of crosslink, substantially higher values of E were obtained.

Difficulties were experienced in all cases in determining the threshold values of tear energy, G_{CO} . As shown in Figure 2, when the tear strength G_C of unswollen samples is plotted as a function of temperature, it appears to reach a lower limit at temperatures of about 120°C or higher, but these values are unexpectedly high, 150 - 500 J/m². Moreover, at temperatures of 150°C or higher the samples showed signs of rapid decomposition. Similar behavior was shown previously by cis-polyisoprene materials (4). It is attributed to the occurrence of strain-induced crystallinity at the tip of the propagating tear, even at temperatures as high as 150°C, which enhances the tear strength markedly.

Values of the tear strength of highly-swollen samples were found to be much lower, comparable to those for other elastomeric materials, and they did not vary significantly with the test temperature over

the range 80°C to 140°C or with the nature of the swelling liquid. These values have therefore been taken as threshold values, although no independent evidence of having reached threshold conditions was obtained.

Polychloroprene, SBR, polysulfide, PB and EPDM

As the results given in Table 2 show, these materials all gave roughly similar values of threshold tear strength, about 50-100 J/m², when crosslinked with oxide, C-C, or simple sulfur crosslinks. Thus, there is no obvious effect of the varied chemical structure of the polymer molecules, or of the crosslinks that connect them, upon the tear strength.

When the values of threshold tear strength for these materials were plotted against the corresponding values of Young's modulus E , Figure 3, using logarithmic scales for both axes, the results were found to be consistent with a linear relationship having a slope of $-1/2$, in accordance with equation 2. Thus, the variations found in the threshold tear strength for these different materials are apparently largely accounted for by variations in the degree of crosslinking. Neither the chemical structure of the polymer chain nor of the crosslinks between them appears to be significant. This is probably because of the close similarity in chain flexibility, bond length, mass per main-chain atom, and bond dissociation energy for these varied systems. However, other systems were found to be significantly stronger, as discussed below. It has previously been shown that polydimethylsiloxanes and phosphonitrilic fluoroelastomers are substantially weaker, because of their greater mass per main-chain atom (4).

Sulfur crosslinking

In Table 2, the symbol $-S_n-$ is used to denote crosslinking systems which yield predominately polysulfidic crosslinks, having more than two sulfur atoms per crosslink. (The symbol $-S_x-$ is used to denote systems which yield crosslinks of unknown structure, but probably with two or fewer sulfur atoms per crosslink.)

The "inefficiently" crosslinked materials, with polysulphidic crosslinks, were found to be significantly stronger than those with monosulfidic, disulfidic or C-C crosslinks. At the same general level of crosslinking, and therefore at similar values of Young's modulus, the threshold tear strength was approximately twice as high.

It has been generally accepted that polysulfidic crosslinks give stronger vulcanizates than monosulfidic or C-C crosslinks (7), but the present measurements are the first ones to be carried out under threshold conditions, as far as the authors are aware. Explanations in terms of enhanced energy dissipation are thus ruled out. Instead, it seems probable that crosslink rearrangement or scission before rupture of the main chain is responsible for the observed strengthening feature (7). In effect, the small-strain elastic properties are those of relatively highly-crosslinked, short-chain, vulcanizates while the tear strengths arise from relatively lightly-crosslinked, long-chain structures, as a result of rearrangement of the original crosslinks under high stresses.

Carbon black reinforcement

The determination of the threshold tear strength for carbon-black-reinforced materials was found to be more difficult than for the corresponding unfilled materials. Low and constant values of tear

strength were only attained in the swollen state and at elevated temperatures. Although these values have been taken to be threshold values, there was no clear proof that threshold conditions had, indeed, been achieved.

The values obtained in this way were found to be considerably higher, about twice as high, as for the corresponding unfilled materials (Table 2), being generally around 200 J/m^2 . Because the reinforced compounds were based on sulfur crosslinking systems yielding polysulfidic crosslinks (as is customary) the corresponding unfilled materials were stronger than the simplest vulcanizates, by another factor of about 2, as discussed previously. Thus, the carbon-black-reinforced materials were 3-4 times stronger than the simplest unreinforced vulcanizate of the same elastomer under threshold conditions.

The large reinforcing effect of carbon black under normal conditions is well-known. It is interesting to note that a substantial degree of reinforcement remains under threshold conditions, when dissipative effects are minimized. It must therefore be ascribed to structural effects. One possible mechanism of reinforcement, analogous to that put forward in connection with polysulfidic crosslinking, would be the detachment of adhering polymer molecules from particles of carbon black at forces somewhat below those causing main-chain fracture. Thus, again, the effective network strand would be initially short, giving a stiff material, but at high stresses it would become longer, and hence give a strong, tear-resistant, material.

Acknowledgements

This work was supported by research grants from General Dynamics Corporation, the Office of Naval Research (Contract N00014-76-C-0408), the Naval Research Laboratory (Contract N00014-82-K-2015), Cabot Corporation, and Lord Kinematics Division of Lord Corporation. The authors are also indebted to J. A. Hartwell, H. J. Kim and R. W. Niebaum for experimental assistance at various times.

References

1. H. K. Mueller and W. G. Knauss, Trans. Soc. Rheol. 15, 217-233 (1971).
2. A. Ahagon and A. N. Gent, J. Polymer Sci. Polymer Phys. Ed. 13, 1903-1911 (1975).
3. A. N. Gent and R. H. Tobias, in "Elastomers and Rubber Elasticity," ed. by J. E. Mark and J. Lal, ACS Symposium Series 193, American Chemical Society, Washington, D.C., 1982, pp. 367-376.
4. A. N. Gent and R. H. Tobias, J. Polymer Sci. Polymer Phys. Ed., in press.
5. G. J. Lake and A. G. Thomas, Proc. Roy. Soc. (London) A300, 108-119 (1967).
6. L. R. G. Treloar, Physics of Rubber Elasticity, 2nd ed., Clarendon Press, Oxford, 1958.
7. E. Southern in "Elastomers: Criteria for Engineering Design," ed. by C. Hepburn and R. J. W. Reynolds, Applied Science Publishers, London, 1979, pp. 273-310.

Table 1. Mix formulations, in parts by weight, and vulcanization conditions employed for preparing test specimens.

Polychloroprene, oxide crosslinks:

Neoprene WRT, 100; magnesium oxide, 2; zinc oxide, 5.

Vulcanized at 150°C for 30, 40 and 90 min.

Polychloroprene, sulfur crosslinks:

Neoprene WRT, 100; sulfur, 2; diorthotolyl guanidine (DOTG), 0.5; tetramethylthiuram disulfide, 1.5. Vulcanized at 140°C for 40 and 80 min.

Polychloroprene, oxide and sulfur crosslinks:

(i) Neoprene WRT, 100; sulfur, 1; tetramethylthiuram monosulfide (TMTM), 1; DOTG, 0.5; magnesium oxide, 4; zinc oxide, 5; stearic acid, 1.

(ii) Neoprene WRT, 100; sulfur 2; TMTM, 1; DOTG, 1; magnesium oxide, 8; zinc oxide, 10.

Both compounds were vulcanized at 150°C for 2 h.

Polysulfide:

(i) Thiokol LP-32, 100; manganese dioxide, 4.

(ii) Thiokol LP-32, 100; manganese dioxide, 10.

Both compounds were vulcanized at 100°C for 1 h.

Table 1 (continued)

SBR:

FR-S 1502, 100; dicumyl peroxide, 0.5. Vulcanized at 150°C for 2 h.

Polybutadiene (PB), carbon-carbon crosslinks:

Diene 35 NFA, 100; dicumyl peroxide, 0.2. Vulcanized at 150°C for 1 h.

Polybutadiene, EV formulation:

Diene 35 NFA, 100; zinc oxide, 5; sulfur, 0.6; zinc 2-ethyl hexanoate, 2; 2-morpholinothiobenzthiazole (Santocure MOR), 1.44; tetrabutylthiuram disulfide, 0.6; Agerite Resin D, 1. Vulcanized at 140°C for 40 min.

Polybutadiene, conventional sulfur recipe:

Diene 35 NFA, 100; zinc oxide, 3.5; stearic acid, 2.5; sulfur, 2; Santocure MOR, 0.6; Philrich oil HA5, 5; phenyl-2-naphthylamine (PBNA); 1. Vulcanized at 150°C for 1 h.

Polybutadiene, carbon-black-reinforced, conventional sulfur recipe:

(i) As the preceding unfilled recipe, plus:

N330 carbon black (Cabot Corporation, Vulcan 3), 50.

(ii) As the preceding unfilled recipe, plus:

N765 carbon black (Cabot Corporation, Sterling black), 50.

Both compounds were vulcanized at 150°C for 1 h.

Table 1 (continued)

Ethylene-propylene copolymer (EPDM), carbon-carbon crosslinks:

Vistalon 4608, 100; dicumyl peroxide, 2. Vulcanized at 160°C
for 2 h.

EPDM, sulfur crosslinks:

Vistalon 4608, 100; sulfur, 1.5; mercaptobenzothiazole, 0.6;
methyl ethyl tuads, 1.5; zinc oxide, 4; stearic acid, 1.
Vulcanized at 150°C for 40 min.

EPDM, carbon-black-reinforced, sulfur crosslinks:

As the preceding unfilled recipe, plus:

N330 carbon black (Cabot Corporation, Vulcan 3), 50.

Vulcanized at 150°C for 40 min.

Table 2. Threshold tear strength G_{co} for various compounds. (The mix formulations and vulcanization conditions are given in the Appendix.)

Elastomer	Crosslink type	Young's modulus E (kPa)	Linear swelling ratio λ_s	G_{co} (J/m ²)
			Swollen with	
Neoprene WRT	-O-	370	TCB 2.58	120
"	"	610	2.32	110
"	"	850	2.17	66
Neoprene WRT	-S _x -	600	2.39	88
"	"	850	2.17	70
Neoprene WRT	-O- and -S _x -	2050	1.6	48
"	"	3200	1.4	65
Thiokol LP-32	-S ₂ -	640	1.71	96
"	"	1010	1.67	66
			Swollen with	
SBR 1502	-C-	2250	paraffin oil 1.20	60
PB (Diene 35 NFA)	-C-	2900	1.30	62
"	-S-(EV)	-	1.32	56
"	-S _n -	-	1.34	106
PB + 50 phr N330 carbon black	-S _n -	-	1.2	200
PB + 50 phr N765 carbon black	-S _n -	-	1.36	<u>ca</u> 200
EPDM (Vistalon 4608)	-C-		1.38	56
"	-S _n -		1.44	<u>ca</u> 160
EPDM + 50 phr N330 carbon black	-S _n -		1.3	210

Figure captions

- Figure 1. Method of measuring tear strength.
- Figure 2. Tear strength G_c vs temperature for polychloroprene and SBR vulcanizates. Polychloroprene oxide crosslinks: $\Delta, \diamond$; sulfur crosslinks: $+, \odot, \square$. SBR, C-C crosslinks: $\circ$
- Figure 3. Threshold tear strength G_{co} vs Young's modulus E . Polychloroprene materials, $\circ$; polysulfide, $\bullet$; polybutadiene, $\bullet$; SBR, $\oplus$. The line is drawn with a slope of $-\frac{1}{2}$.

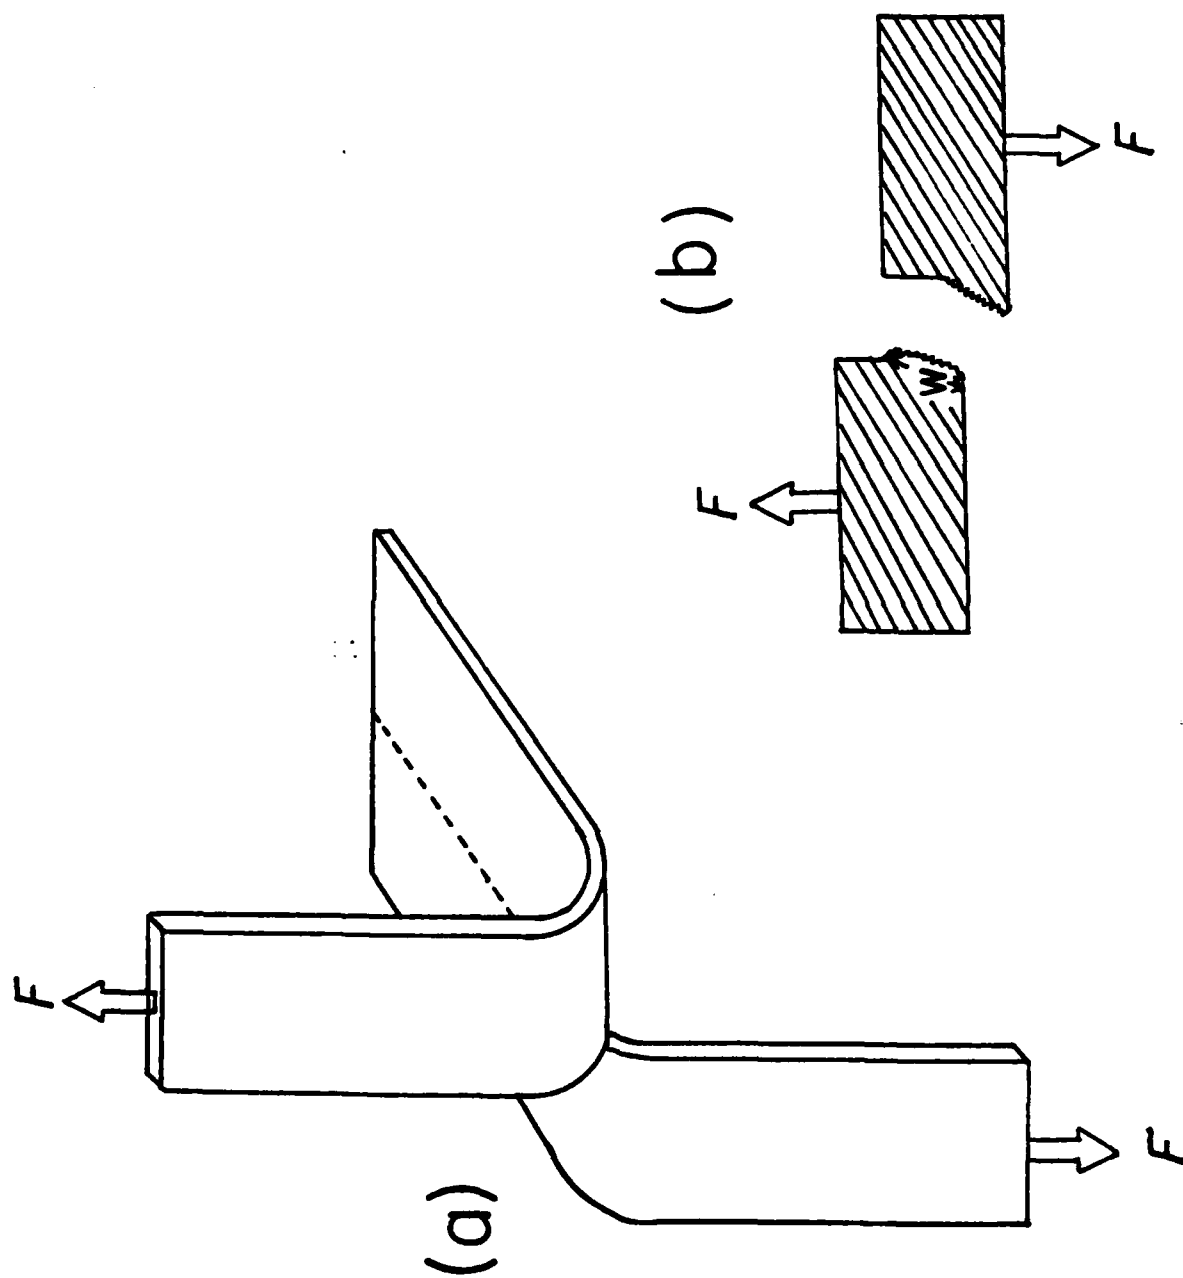


FIGURE 1

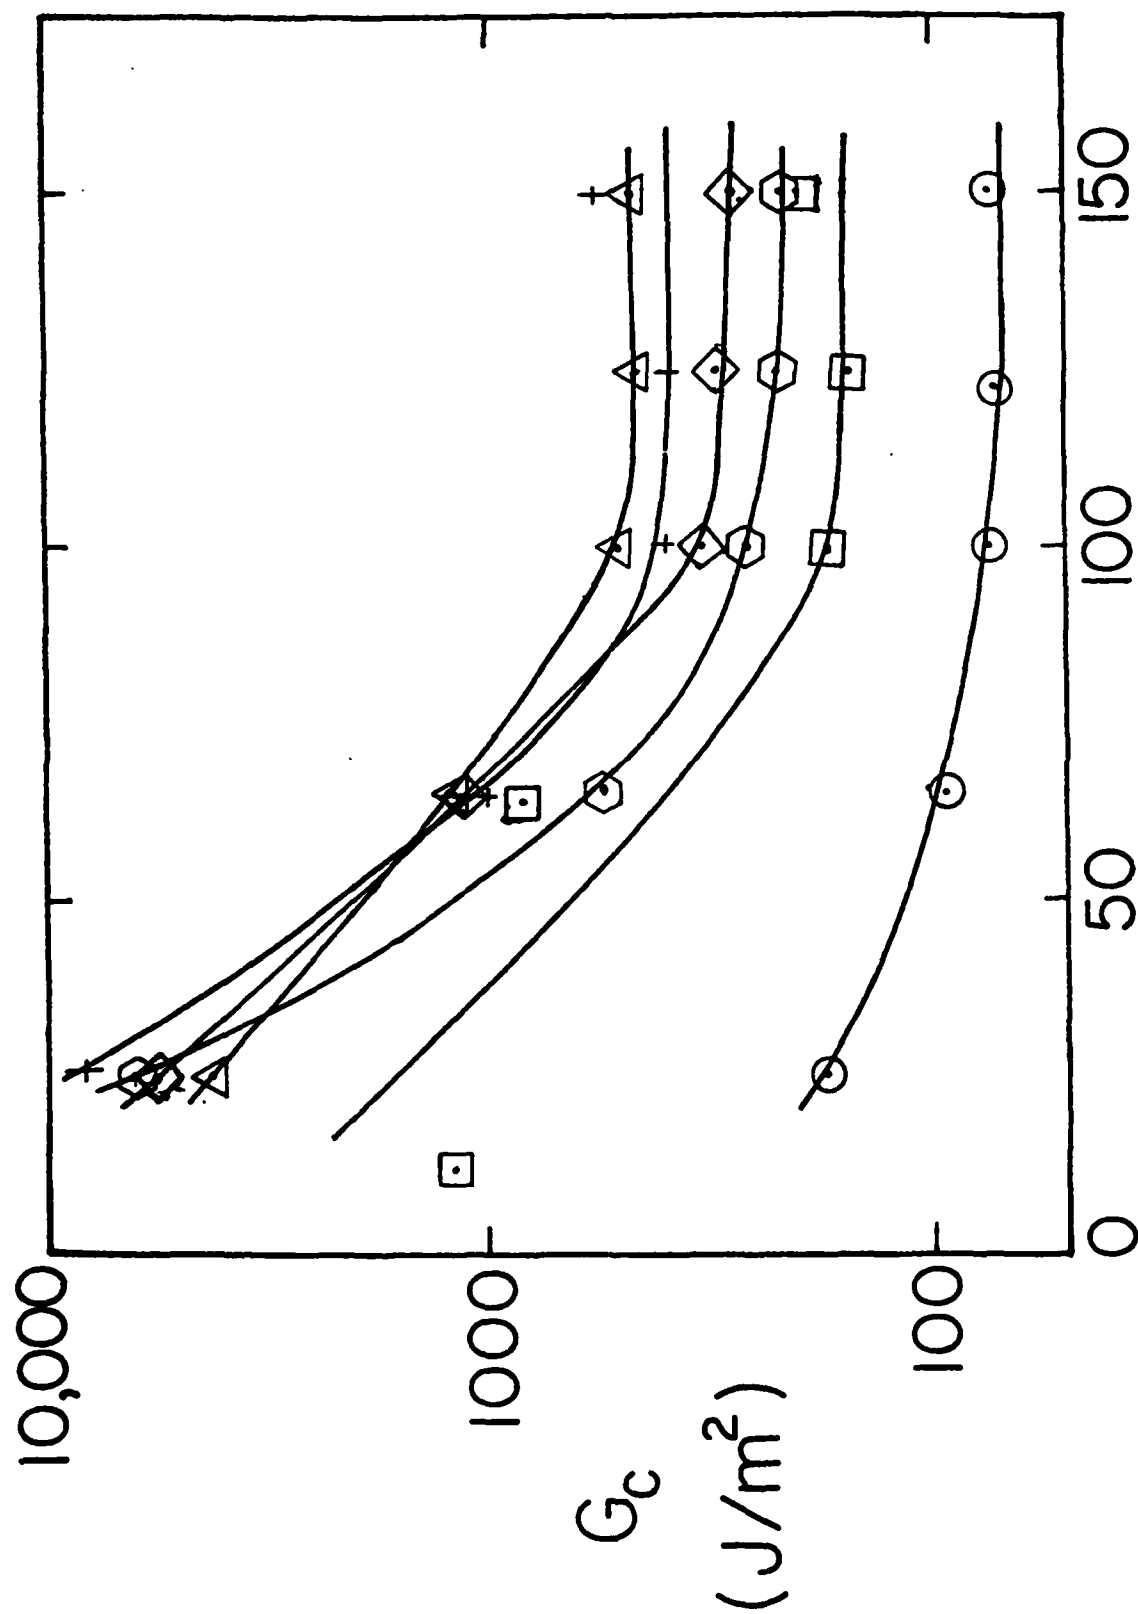


FIGURE 2

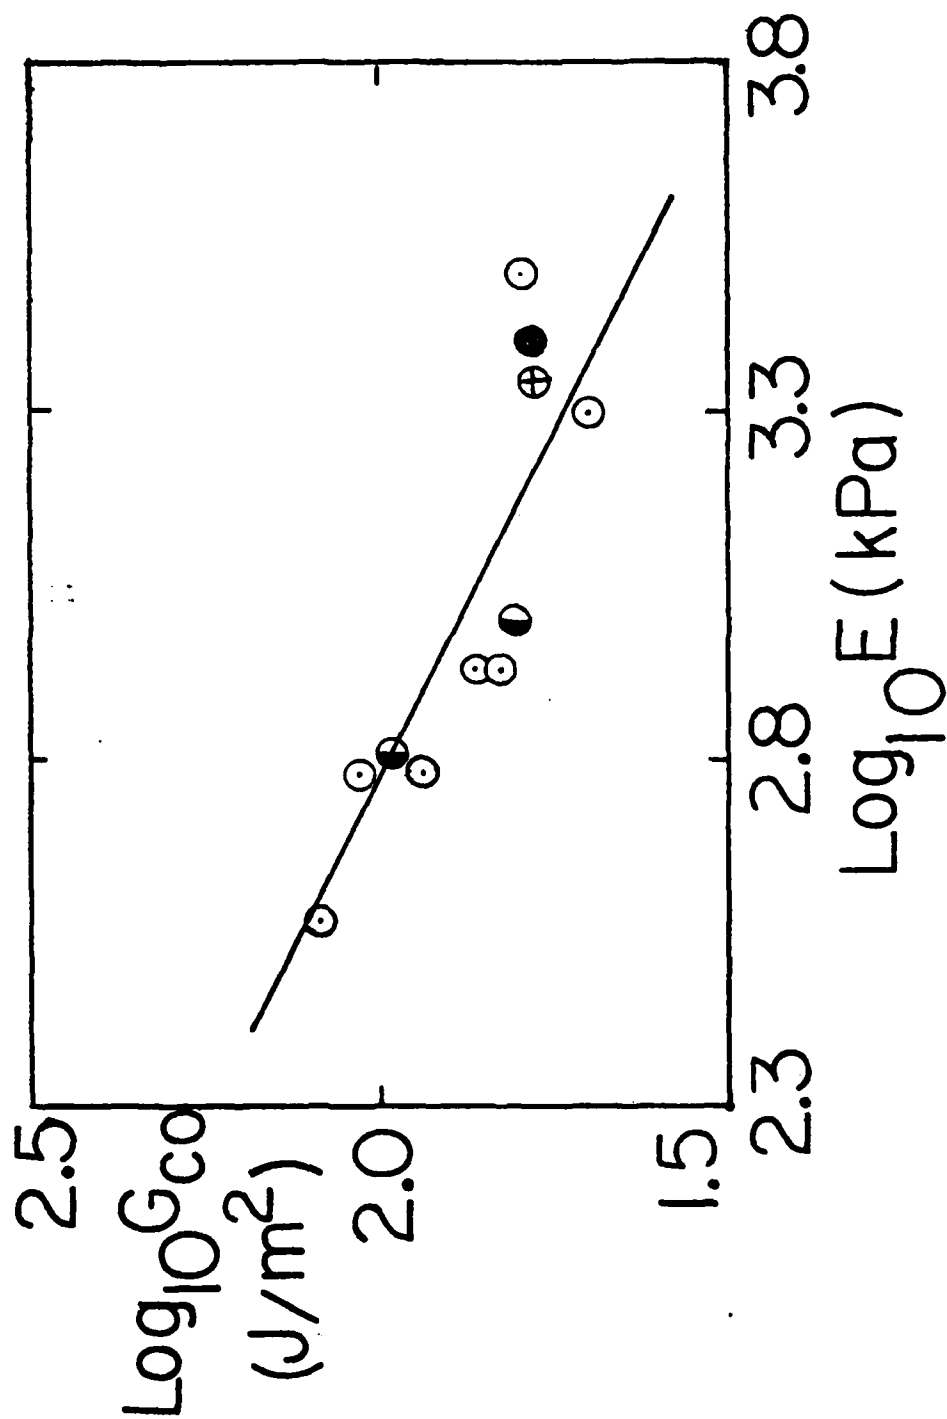


FIGURE 3

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. L.V. Schmidt Assistant Secretary of the Navy (R,E, and S) Room 5E 731 Pentagon Washington, D.C. 20350	1	Dr. F. Roberto Code AFRPL MKPA Edwards AFB, CA 93523	1
Dr. A.L. Slafkosky Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1	Dr. L.H. Caveny Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, D.C. 20332	1
Dr. Richard S. Miller Office of Naval Research Code 413 Arlington, VA 22217	10	Mr. Donald L. Ball Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, D.C. 20332	1
Mr. David Siegel Office of Naval Research Code 260 Arlington, VA 22217	1	Dr. John S. Wilkes, Jr. FJSRL/NC USAF Academy, CO 80840	1
Dr. R.J. Marcus Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106	1	Dr. R.L. Lou Aerojet Strategic Propulsion Co. P.O. Box 15699C Sacramento, CA 95813	1
Dr. Larry Peebles Office of Naval Research East Central Regional Office 666 Summer Street, Bldg. 114-D Boston, MA 02210	1	Dr. V.J. Keenan Anal-Syn Lab Inc. P.O. Box 547 Pacif, PA 19301	1
Dr. Phillip A. Miller Office of Naval Research San Francisco Area Office One Hallidie Plaza, Suite 601 San Francisco, CA 94102	1	Dr. Philip Howe Army Ballistic Research Labs ARRADCOM Code DRDAR-3LT Aberdeen Proving Ground, MD 21005	1
Mr. Otto K. Heiney AFATL - DLDL Elgin AFB, FL 32542	1	Mr. L.A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1
Mr. R. Geisler ATTN: MKP/MS24 AFRPL Edwards AFB, CA 93523	1	Dr. W.W. Wharton Attn: DRSMI-RKL Commander U.S. Army Missile Command Redstone Arsenal, AL 35898	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. R.G. Rhoades Commander Army Missile Command DRSMI-R Redstone Arsenal, AL 35898	1	Dr. E.H. Debutts Hercules Inc. Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. W.D. Stephens Atlantic Research Corp. Pine Ridge Plant 7511 Wellington Rd. Gainesville, VA 22065	1	Dr. James H. Thacher Hercules Inc. Magna Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. A.W. Barrows Ballistic Research Laboratory USA ARADCOM DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Mr. Theodore M. Gilliland Johns Hopkins University APL Chemical Propulsion Info. Agency Johns Hopkins Road Laurel, MD 20810	1
Dr. C.M. Frey Chemical Systems Division P.O. Box 358 Sunnyvale, CA 94086	1	Dr. R. McGuire Lawrence Livermore Laboratory University of California Code L-324 Livermore, CA 94550	1
Professor F. Rodriguez Cornell University School of Chemical Engineering Olin Hall, Ithaca, N.Y. 14853	1	Dr. Jack Linsk Lockheed Missiles & Space Co. P.O. Box 504 Code Org. 83-10, Bldg. 154 Sunnyvale, CA 94088	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Dr. B.G. Craig Los Alamos National Lab P.O. Box 1663 NSP/DOD, MS-245 Los Alamos, NM 87545	1
Dr. Rocco C. Musso Hercules Aerospace Division Hercules Incorporated Allegheny Ballistic Lab P.O. Box 210 Washington, D.C. 21502	1	Dr. R.L. Rabie WX-2, MS-952 Los Alamos National Lab. P.O. Box 1663 Los Alamos NM 37545	1
Dr. Ronald L. Simmons Hercules Inc. Eglin AFATL/DLCL Eglin AFB, FL 32542	1	Dr. R. Rogers, WX-2 Los Alamos Scientific Lab. P.O. Box 1663 Los Alamos, NM 87545	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. R. Brown Naval Air Systems Command Code 330 Washington, D.C. 20361	1	Dr. J. Schnur Naval Research Lab. Code 6510 Washington, D.C. 20375	1
Dr. H. Rosenwasser Naval Air Systems Command AIR-310C Washington, D.C. 20360	1	Mr. R. Beauregard Naval Sea Systems Command SEA 64E Washington, D.C. 20362	1
Mr. B. Sobers Naval Air Systems Command Code 03P25 Washington, D.C. 20360	1	Mr. G. Edwards Naval Sea Systems Command Code 62R3 Washington, D.C. 20362	1
Dr. L.R. Rothstein Assistant Director Naval Explosives Dev. Engineering Dept. Naval Weapons Station Yorktown, VA 23691	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, PA 19112	1
Dr. Lionel Dickinson Naval Explosive Ordnance Disposal Tech. Center Code D Indian Head, MD 20640	1	Dr. H.G. Adolph Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1
Mr. C.L. Adams Naval Ordnance Station Code PM4 Indian Head, MD 20640	1	Dr. T.D. Austin Naval Surface Weapons Center Code R16 Indian Head, MD 20640	1
Mr. S. Mitchell Naval Ordnance Station Code 5253 Indian Head, MD 20640	1	Dr. T. Hall Code R-11 Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910	1
Dr. William Tolles Dean of Research Naval Postgraduate School Monterey, CA 93940	1	Mr. G.L. Mackenzie Naval Surface Weapons Center Code R101 Indian Head, MD 20640	1
Naval Research Lab. Code 6100 Washington, D.C. 20375	1	Dr. K.F. Mueller Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. J. Murrin Naval Sea Systems Command Code 62R2 Washington, D.C. 20362	1	Dr. A. Nielsen Naval Weapons Center Code 385 China Lake, CA 93555	1
Dr. D.J. Pastine Naval Surface Weapons Center Code R04 White Oak Silver Spring, MD 20910	1	Dr. R. Reed, Jr. Naval Weapons Center Code 388 China Lake, CA 93555	1
Mr. L. Roslund Naval Surface Weapons Center Code R122 White Oak, Silver Spring MD 20910	1	Dr. L. Smith Naval Weapons Center Code 3205 China Lake, CA 93555	1
Mr. M. Stosz Naval Surface Weapons Center Code R121 White Oak Silver Spring, MD 20910	1	Dr. B. Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1
Dr. E. Zimmet Naval Surface Weapons Center Code R13 White Oak Silver Spring, MD 20910	1	Dr. A. Faulstich Chief of Naval Technology MAT Code 0716 Washington, D.C. 20360	1
Dr. D. R. Derr Naval Weapons Center Code 388 China Lake, CA 93555	1	LCDR J. Walker Chief of Naval Material Office of Naval Technology MAT, Code 0712 Washington, D.C. 20360	1
Mr. Lee N. Gilbert Naval Weapons Center Code 3205 China Lake, CA 93555	1	Mr. Joe McCartney Naval Ocean Systems Center San Diego, CA 92152	1
Dr. E. Martin Naval Weapons Center Code 3858 China Lake, CA 93555	1	Dr. S. Yamamoto Marine Sciences Division Naval Ocean Systems Center San Diego, CA 91232	1
Mr. R. McCarten Naval Weapons Center Code 3272 China Lake, CA 93555	1	Dr. G. Bosmajian Applied Chemistry Division Naval Ship Research & Development Center Annapolis, MD 21401	1
		Dr. H. Shuey Rohn and Haas Company Huntsville, Alabama 35801	1

DISTRIBUTION LIST

<u>No. Copies</u>	<u>No. Copies</u>
Dr. J.F. Kincaid Strategic Systems Project Office Department of the Navy Room 901 Washington, D.C. 20376	1
Strategic Systems Project Office Propulsion Unit Code SP2731 Department of the Navy Washington, D.C. 20376	1
Mr. E.L. Throckmorton Strategic Systems Project Office Department of the Navy Room 1048 Washington, D.C. 20376	1
Dr. D.A. Flanigan Thiokol Huntsville Division Huntsville, Alabama 35807	1
Mr. G.F. Mangum Thiokol Corporation Huntsville Division Huntsville, Alabama 35807	1
Mr. E.S. Sutton Thiokol Corporation Elkton Division P.O. Box 241 Elkton, MD 21921	1
Dr. G. Thompson Thiokol Wasatch Division MS 240 P.O. Box 524 Brigham City, UT 84302	1
Dr. T.F. Davidson Technical Director Thiokol Corporation Government Systems Group P.O. Box 9253 Ogden, Utah 84409	1
Dr. C.W. Vriesen Thiokol Elkton Division P.O. Box 241 Elkton, MD 21921	1
Dr. J.C. Hinshaw Thiokol Wasatch Division P.O. Box 524 Brigham City, Utah 84302	1
U.S. Army Research Office Chemical & Biological Sciences Division P.O. Box 12211 Research Triangle Park NC 27709	1
Dr. R.F. Walker USA ARRADCOM DRDAR-LCE Dover, NJ 07801	1
Dr. T. Sinden Munitions Directorate Propellants and Explosives Defence Equipment Staff British Embassy 3100 Massachusetts Ave. Washington, D.C. 20003	1
LTC B. Loving AFROL/LK Edwards AFB, CA 93523	1
Professor Alan N. Gent Institute of Polymer Science University of Akron Akron, OH 44325	1
Mr. J. M. Frankle Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1

DISTRIBUTION LIST

<u>No. Copies</u>		<u>No. Copies</u>	
1	Dr. Ingo W. May Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1	Dr. J. P. Marshall Dept. 52-35, Bldg. 204/2 Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304
1	Professor N.W. Tschoegl California Institute of Tech Dept. of Chemical Engineering Pasadena, CA 91125	1	Ms. Joan L. Janney Los Alamos National Lab Mail Stop 920 Los Alamos, NM 87545
1	Professor M.D. Nicol University of California Dept. of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024	1	Dr. J. M. Walsh Los Alamos Scientific Lab Los Alamos, NM 87545
1	Professor A. G. Evans University of California Berkeley, CA 94720	1	Professor R. W. Armstrong Univ. of Maryland Department of Mechanical Eng. College Park, MD 20742
1	Professor T. Litovitz Catholic Univ. of America Physics Department 520 Michigan Ave., N.E. Washington, D.C. 20017	1	Prof. Richard A. Reinhardt Naval Postgraduate School Physics & Chemistry Dept. Monterey, CA 93940
1	Professor W. G. Knauss Graduate Aeronautical Lab California Institute of Tech. Pasadena, CA 91125	1	Dr. R. Bernecker Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910
1	Professor Edward Price Georgia Institute of Tech. School of Aerospace Engin. Atlanta, Georgia 30332	1	Dr. M. J. Kamlet Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910
1	Dr. Kenneth O. Hartman Hercules Aerospace Division Hercules Incorporated P.O. Box 210 Cumberland, MD 21502	1	Professor J. D. Achenbach Northwestern University Dept. of Civil Engineering Evanston, IL 60201
1	Dr. Thor L. Smith IBM Research Lab 042.282 San Jose, CA 95193	1	Dr. N. L. Basdekas Office of Naval Research Mechanics Program, Code 432 Arlington, VA 22217
		1	Professor Kenneth Kuo Pennsylvania State Univ. Dept. of Mechanical Engineering University Park, PA 16802

DISTRIBUTION LIST

	<u>No. Copies</u>	<u>No. Copies</u>
Dr. S. Sheffield Sandia Laboratories Division 2513 P.O. Box 5800 Albuquerque, NM 87185	1	
Dr. M. Farber Space Sciences, Inc. 135 Maple Avenue Monrovia, CA 91016	1	
Dr. Y. M. Gupta SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Mr. M. Hill SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Professor Richard A. Schapery Texas A&M Univ. Dept of Civil Engineering College Station, TX 77843	1	
Dr. Stephen Swanson Univ. of Utah Dept. of Mech. & Industrial Engineering MEB 3008 Salt Lake City, UT 84112	1	
Mr. J. D. Byrd Thiokol Corp. Huntsville Huntsville Div. Huntsville, AL 35807	1	
Professor G. D. Duval Washington State University Dept. of Physics Pullman, WA 99163	1	
Prof. T. Dickinson Washington State University Dept. of Physics Pullman, WA 99163	1	